

LOG NO:	JUN 28 1993	RD.
ACTION:		
FILE NO:		

VOLUME 2
ASSESSMENT REPORT FOR 1992-1993
DRILLING ON THE HUCKLEBERRY "MAIN ZONE"
(LEN 4, 6, 15, 17, 19 AND
LEN GROUP NO. 29 CLAIMS)
OMINECA MINING DIVISION
N.T.S 93 E/11E
53° 41'N; 127° 10'W

OWNER: KENNECOTT CANADA INC.
OPERATOR: NEW CANAMIN RESOURCES LTD.
CONSULTANT: AINSWORTH-JENKINS HOLDINGS INC.
AUTHOR: DAVID M. JENKINS, PGeo

MAY 15, 1993



GEOLOGICAL BRANCH
ASSESSMENT REPORT

22,928

VOLUME 2

APPENDIX II ANALYSES OF CORE SAMPLES



**MINERAL
• ENVIRONMENTS
LABORATORIES**

Division of Assayers Corp. Ltd.

Cu Assay Procedure:

Samples are dried @ 95C and when dry are crushed on a jaw crusher. The -1/4 inch output of the jaw crusher is put through a secondary roll crusher to reduce it to -15 mesh. The whole sample is then riffled on a Jones Riffle down to a statistically representative 500 gram sub-sample (in accordance with Gy's statistical rules.) This sub-sample is then pulverized in a ring pulverizer to 95% minus 120 mesh, rolled and bagged for analysis. The remaining reject from the Jones Riffle is bagged and stored.

A 2.000 gram sub-sample is weighed from the pulp bag for analysis. Each batch of 70 assays has a natural standard and a reagent blank included. The assays are digested using a HNO₃ - KClO₄ mixture and when reaction subsides, HCL is added to assay before it is placed on a hotplate to digest. After digestion is complete the assays are cooled, diluted to volume and mixed.

The assays are analyzed on atomic absorption spectrometers using the appropriate standard sets. The natural standard digested along with this set must be within 2 standard deviations of it's known or the whole set is re-assayed. If any of the assays are >1% they are re-assayed at a lower weight.



MIN
• EN
LABORATORIES

Assess. ICP

Division of Assayers Corp. Ltd.

ANALYTICAL PROCEDURE REPORT FOR ASSESSMENT WORK:

PROCEDURE FOR TRACE ELEMENT ICP

Ag, Al, As, B, Ba, Be, Bi, Ca, Cd, Co, Cu, Fe, K, Li, Mg, Mn, Mo, Na,
Ni, P, Pb, Sb, Sr, Th, Ti, V, Zn, Ga, Sn, W, Cr

Samples are processed by Min-En Laboratories at 705 West 15th St., North Vancouver B.C. employing the following procedures.

After drying the samples at 95 degrees C, the soil and stream sediment samples are screened by 80 mesh sieve to obtain the -80 mesh fraction for analysis. The rock samples are crushed by jaw crusher to approximately 1/4 inch, then passed through a rolls crusher that further reduces the size to approx. -10 mesh. The sample is then pulverized on a ring mill pulverizer.

0.50 gram of the sample is digested for 2 hours with an aqua regia mixture. After cooling, the sample is diluted to standard volume.

The solutions are analysed by computer operated Jarrell Ash 9000 ICAP or Jobin Yvon Type II Inductively Coupled Plasma Spectrophotometers.



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:
3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

2S-0289-RA1

Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attn: **B.AINSWORTH/A.SAVAGE/D.JENKINS**

Date: **SEP-04-92**
Copy 1. **NEW CANAMIN RESOURCES LTD., N.VANC, BC**
2. **AINSWORTH-JENKINS C/O MIN-EN SMITHERS**

We hereby certify the following Assay of 24 CORE samples submitted AUG-28-92 by D. JENKINS.

Sample Number	Cu %
0-40551	.151
0-40552	.404
0-40553	.345
0-40554	.399
0-40555	.377
0-40556	.281
0-40557	.292
0-40558	.320
0-40559	.647
0-40560	.323
0-40561	.276
0-40562	.294
0-40563	.477
0-40564	.273
0-40565	.369
0-40566	.402
0-40567	.277
0-40568	.158
0-40569	.089
0-40570	.056
0-40571	.103
0-40572	.140
0-40573	.141
0-40574	.135

Certified by 
MIN-EN LABORATORIES



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:
3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

2S-0289-RA2

Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attn: **B. AINSWORTH/A. SAVAGE/D. JENKINS**

Date: **SEP-04-92**
Copy 1. **NEW CANAMIN RESOURCES LTD., N. VANC, BC**
2. **AINSWORTH-JENKINS C/O MIN-EN SMITHERS**

We hereby certify the following Assay of 22 CORE samples submitted AUG-28-92 by D. JENKINS.

Sample Number	Cu %
0-40575	.147
0-40576	.270
0-40577	.120
0-40578	.151
0-40579	.153
0-40580	.325
0-40581	.198
0-40582	.353
0-40583	.609
0-40584	.678
0-40585	.688
0-40586	.315
0-40587	.546
0-40588	.640
0-40589	.218
0-40590	.347
0-40591	.860
0-40592	.441
0-40593	.368
0-40594	.339
0-40595	.227
0-40596	.342

Certified by _____

MIN-EN LABORATORIES

II - 4



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:

705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:

3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

2S-0298-RA1

Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attn: **B. AINSWORTH/D. JENKINS/A. SAVAGE**

Date: **SEP-09-92**

Copy 1. NEW CANAMIN RES., NORTH VANCOUVER, B.C. **
2. AINSWORTH-JENKINS, C/O MIN-EN, SMITHERS.

We hereby certify the following Assay of 24 CORE samples submitted SEP-01-92 by DAVE JENKINS.

Sample Number	Cu %
0-40601	.522
0-40602	.382
0-40603	.198
0-40604	.171
0-40605	.275
0-40606	.120
0-40607	.254
0-40608	.300
0-40609	.259
0-40610	.176
0-40611	.282
0-40612	.256
0-40613	.325
0-40614	.431
0-40615	.490
0-40616	.700
0-40617	.389
0-40618	.404
0-40619	.657
0-40620	.830
0-40621	1.160
0-40622	.890
0-40623	.880
0-40624	.840

Certified by 

MIN-EN LABORATORIES

II-5



MIN-EN LABORATORIES
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:
3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

2S-0298-RA2

Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attn: **B.AINSWORTH/D.JENKINS/A.SAVAGE**

Date: **SEP-09-92**
Copy 1. **NEW CANAMIN RES., NORTH VANCOUVER, B.C.**
2. **AINSWORTH-JENKINS, C/O MIN-EN, SMITHERS.**

We hereby certify the following Assay of 24 CORE samples submitted SEP-01-92 by DAVE JENKINS.

Sample Number	Cu %
0-40625	.538
0-40626	1.270
0-40627	1.070
0-40628	.840
0-40629	.584
0-40630	.557
0-40631	.481
0-40632	.416
0-40633	.283
0-40634	.184
0-40635	.123
0-40636	.174
0-40637	.338
0-40638	.319
0-40639	.309
0-40640	.286
0-40641	.216
0-40642	.259
0-40643	.213
0-40644	.326
0-40645	.314
0-40646	.272
0-40647	.214
0-40648	.204

Certified by 

MIN-EN LABORATORIES

II - C



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:
3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

2S-0298-RA3

Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attn: **B.AINSWORTH/D.JENKINS/A.SAVAGE**

Date: **SEP-09-92**

Copy 1. **NEW CANAMIN RES., NORTH VANCOUVER, B.C.**
2. **AINSWORTH-JENKINS, C/O MIN-EN, SMITHERS.**

We hereby certify the following Assay of 1 CORE samples submitted SEP-01-92 by DAVE JENKINS.

Sample Number	Cu %
0-40649	.308

Certified by _____

MIN-EN LABORATORIES

II - 7



MIN-EN LABORATORIES
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:
3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

2S-0304-RA1

Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attn: **B.AINSWORTH/A.SAVAGE/D.JENKINS**

Date: **SEP-16-92**
Copy 1. **NEW CANAMIN RESOURCES LTD. VANCOUVER**
2. **AINSWORTH-JENKINS C/O MIN-EN SMITHERS**

We hereby certify the following Assay of 24 CORE samples submitted SEP-08-92 by DAVID M. JENKINS.

Sample Number	Cu %
40651	.546
40652	.570
40653	.463
40654	.642
40655	.517
40656	.486
40657	.631
40658	.801
40659	.550
40660	.433
40661	.834
40662	.493
40663	.641
40664	.538
40665	.567
40666	.408
40667	.305
40668	.235
40669	.224
40670	.239
40671	.414
40672	.303
40673	.278
40674	.404

Certified by 

MIN-EN LABORATORIES

II - e



MIN-EN LABORATORIES
 (DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
 CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
 705 WEST 15TH STREET
 NORTH VANCOUVER, B.C. CANADA V7M 1T2
 TELEPHONE (604) 980-5814 OR (604) 988-4524
 FAX (604) 980-9621

SMITHERS LAB.:
 3176 TATLOW ROAD
 SMITHERS, B.C. CANADA V0J 2N0
 TELEPHONE (604) 847-3004
 FAX (604) 847-3005

Assay Certificate

2S-0304-RA2

Company: **NEW CANAMIN RESOURCES LTD.**
 Project: **HUCKLEBERRY**
 Attn: **B.AINSWORTH/A.SAVAGE/D.JENKINS**

Date: **SEP-16-92**
 Copy 1. **NEW CANAMIN RESOURCES LTD. VANCOUVER**
 2. **AINSWORTH-JENKINS C/O MIN-EN SMITHERS**

We hereby certify the following Assay of 24 CORE samples submitted SEP-08-92 by DAVID M. JENKINS.

Sample Number	Cu %
40675	.206
40676	.265
40677	.281
40678	.273
40679	.179
40680	.158
40701	.249
40702	.603
40703	.381
40704	.828
40705	.475
40706	.690
40707	.474
40708	.232
40709	.294
40710	.286
40711	.388
40712	.142
40713	.137
40714	.201
40715	.308
40716	.121
40717	.261
40718	.365

Certified by 

MIN-EN LABORATORIES



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:

705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:

3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

2S-0304-RA3

Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attn: **B.AINSWORTH/A.SAVAGE/D.JENKINS**

Date: **SEP-16-92**

Copy 1. **NEW CANAMIN RESOURCES LTD. VANCOUVER**
2. **AINSWORTH-JENKINS C/O MIN-EN SMITHERS**

We hereby certify the following Assay of 24 CORE samples submitted SEP-08-92 by DAVID M. JENKINS.

Sample Number	Cu %
40719	.403
40720	.230
40721	.168
40722	.218
40723	.311
40724	.202
40725	.298
40726	.490
40727	.397
40728	.603
40729	.373
40730	.494
40731	.799
40732	.800
40733	.833
40734	.980
40735	1.170
40736	.459
40737	.483
40738	.555
40739	.562
40740	.434
40741	.355
40742	.409

Certified by 

MIN-EN LABORATORIES

II-10



MIN-EN LABORATORIES
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:

705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:

3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

2S-0304-RA4

Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attn: **B.AINSWORTH/A.SAVAGE**

Date: **SEP-17-92**

Copy 1. **NEW CANAMIN RESOURCES LTD. VANCOUVER**
2. **AINSWORTH-JENKINS C/O MIN-EN SMITHERS**

We hereby certify the following Assay of 24 CORE samples submitted SEP-08-92 by DAVID M. JENKINS.

Sample Number	Cu %
40743	.514
40744	.802
40745	1.660
40746	.980
40751	.243
40752	.800
40753	.698
40754	.598
40755	.840
40756	.518
40757	.397
40758	.550
40759	.432
40760	.847
40761	.860
40762	.461
40763	.683
40764	.777
40765	.458
40766	.368
40767	.656
40768	.290
40769	.319
40770	.437

Certified by 
MIN-EN LABORATORIES

II - 11



**MINERAL
ENVIRONNEMENTS
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:
3178 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

2S-0304-RA5

Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attn: **B.AINSWORTH/A.SAVAGE/D.JENKINS**

Date: **SEP-16-92**
Copy 1. **NEW CANAMIN RESOURCES LTD. VANCOUVER**
2. **AINSWORTH-JENKINS C/O MIN-EN SMITHERS**

We hereby certify the following Assay of 24 CORE samples submitted SEP-08-92 by DAVID M. JENKINS.

Sample Number	CU %
40771	.661
40772	.500
40773	.637
40774	.880
40775	.940
40776	.644
40777	.764
40778	.436
40779	.635
40780	.596
40781	.815
40782	.365
40783	.460
40784	.457
40785	.709
40786	.466
40787	.554
40788	.670
40789	.502
40790	.488
40791	.262
40792	.483
40793	.381
40794	.455

Certified by 
MIN-EN LABORATORIES

II-12



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:
3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate


2S-0304-RA6

Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attn: **B.AINSWORTH/A.SAVAGE**

Date: **SEP-17-92**
Copy 1. **NEW CANAMIN RESOURCES LTD. VANCOUVER**
2. **AINSWORTH-JENKINS C/O MIN-EN SMITHERS**

We hereby certify the following Assay of 24 CORE samples submitted SEP-08-92 by DAVID M. JENKINS.

Sample Number	Cu %
40795	.203
40796	.294
40797	.252
40801	.505
40802	.850
40803	1.020
40804	.860
40805	.502
40806	.597
40807	1.210
40808	.847
40809	.850
40810	.816
40811	.476
40812	.356
40813	.406
40814	.586
40815	.490
40816	.447
40817	.285
40818	.302
40820	.870
40821	.357
40822	.257

Certified by 

MIN-EN LABORATORIES



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:
3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

2S-0304-RA7

Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attn: **B.AINSWORTH/A.SAVAGE/D.JENKINS**

Date: **SEP-16-92**
Copy 1. **NEW CANAMIN RESOURCES LTD. VANCOUVER**
2. **AINSWORTH-JENKINS C/O MIN-EN SMITHERS**

We hereby certify the following Assay of 3 CORE samples submitted SEP-08-92 by DAVID M. JENKINS.

Sample Number	Cu %
40823	.269
40824	.177
40825	.155

Certified by _____

MIN-EN LABORATORIES

II-14



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:
3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate


2S-0310-RA1

Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attn: **B.AINSWORTH/A.SAVAGE**

Date: **SEP-18-92**
Copy 1. **NEW CANAMIN RESOURCES LTD. VANCOUVER**
2. **AINSWORTH-JENKINS C/O MIN-EN SMITHERS**

We hereby certify the following Assay of 24 CORE samples submitted SEP-09-92 by DAVE JENKINS.

Sample Number	Cu %
0-40851	.836
0-40852	.491
0-40853	.647
0-40854	.880
0-40855	.770
0-40856	.396
0-40857	.674
0-40858	.850
0-40859	.830
0-40860	.552
0-40861	.597
0-40862	.384
0-40863	.440
0-40864	.355
0-40865	.840
0-40866	.661
0-40867	.423
0-40868	.678
0-40869	.592
0-40870	.500
0-40871	.555
0-40872	.828
0-40873	.623
0-40874	.377

Certified by 

MIN-EN LABORATORIES

II-15



**MIN
EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:
3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

2S-0310-RA2

Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attn: **B.AINSWORTH/A.SAVAGE**

Date: **SEP-18-92**
Copy 1. **NEW CANAMIN RESOURCES LTD. VANCOUVER**
2. **AINSWORTH-JENKINS C/O MIN-EN SMITHERS**

We hereby certify the following Assay of 24 CORE samples submitted SEP-09-92 by DAVE JENKINS.

Sample Number	Cu %
0-40875	.410
0-40876	.457
0-40877	.525
0-40878	.387
0-40879	.692
0-40880	.542
0-40881	.376
0-40882	.387
0-40883	.319
0-40884	.419
0-40885	.317
0-40886	.523
0-40887	.404
0-40901	.357
0-40902	.358
0-40903	.162
0-40904	.378
0-40905	.181
0-40906	.240
0-40907	.680
0-40908	.395
0-40909	.537
0-40910	.320
0-40911	.427

Certified by _____

MIN-EN LABORATORIES

II-16



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:
3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate


2S-0310-RA3

Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attn: **B.AINSWORTH/A.SAVAGE**

Date: **SEP-18-92**
Copy 1. **NEW CANAMIN RESOURCES LTD. VANCOUVER**
2. **AINSWORTH-JENKINS C/O MIN-EN SMITHERS**

We hereby certify the following Assay of 10 CORE samples submitted SEP-09-92 by DAVE JENKINS.

Sample Number	Cu %
0-40912	.386
0-40913	.408
0-40914	.413
0-40915	.339
0-40916	.437
0-40917	.616
0-40918	.402
0-40919	.417
0-40920	.455
0-40921	.207

Certified by 

MIN-EN LABORATORIES

II-17



MIN-EN LABORATORIES
 (DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
 CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:

705 WEST 15TH STREET
 NORTH VANCOUVER, B.C. CANADA V7M 1T2
 TELEPHONE (604) 980-5814 OR (604) 988-4524
 FAX (604) 980-9621

SMITHERS LAB.:

3176 TATLOW ROAD
 SMITHERS, B.C. CANADA V0J 2N0
 TELEPHONE (604) 847-3004
 FAX (604) 847-3005

Assay Certificate

2S-0322-RA1

Company: **NEW CANAMIN RESOURCES LTD.**
 Project: **HUCKLEBERRY**
 Attn: **B.AINSWORTH/A.SAVAGE/D.JENKINS**

Date: **SEP-22-92**

Copy 1. **NEW CANAMIN RESOURCES, N.VANCOUVER, B**
 2. **AINSWORTH-JENKINS C/O MIN-EN SMITHERS**

We hereby certify the following Assay of 24 CORE samples submitted SEP-15-92 by DAVE JENKINS.

Sample Number	Cu %
40922	.168
40923	.137
40924	.172
40925	.115
40951	.149
40952	.304
40953	.408
40954	.288
40955	.340
40956	.275
40957	.321
40958	.348
40959	.417
40960	.521
40961	.449
40962	.403
40963	.475
40964	.402
40965	.544
40966	.439
40967	.612
40968	.761
40969	.815
15001	.500

Certified by _____

MIN-EN LABORATORIES



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:
3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate


2S-0322-RA2

Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attn: **B.AINSWORTH/A.SAVAGE/D.JENKINS**

Date: **SEP-22-92**
Copy 1. **NEW CANAMIN RESOURCES, N.VANCOUVER, B**
2. **AINSWORTH-JENKINS C/O MIN-EN SMITHERS**

We hereby certify the following Assay of 24 CORE samples
submitted SEP-15-92 by DAVE JENKINS.

Sample Number	Cu %
15002	.318
15003	.347
15004	.339
15005	.844
15006	1.090
15007	.754
15008	.428
15009	.334
15010	.354
15011	.168
15012	.408
15013	.389
15014	.611
15015	.425
15016	.370
15017	.430
15018	.398
15019	.677
15020	.588
15021	.217
15022	.294
15023	.656
15024	.459
15025	.800

Certified by 

MIN-EN LABORATORIES



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:
3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

2S-0322-RA3

Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attn: **B.AINSWORTH/A.SAVAGE/D.JENKINS**

Date: **SEP-22-92**
Copy 1. **NEW CANAMIN RESOURCES, N.VANCOUVER, B**
2. **AINSWORTH-JENKINS C/O MIN-EN SMITHERS**

We hereby certify the following Assay of 24 CORE samples submitted SEP-15-92 by DAVE JENKINS.

Sample Number	Cu %
15026	1.040
15027	.960
15028	.856
15029	.747
15030	.782
15031	.724
15032	1.050
15033	.511
15034	.602
15035	1.060
15036	.695
15037	.342
15038	.229
15051	.545
15052	.402
15053	.525
15054	1.090
15055	.351
15056	.602
15057	.440
15058	.551
15059	.582
15060	.457
15061	.521

Certified by _____ 

MIN-EN LABORATORIES

II-20



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:
3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

2S-0322-RA4

Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attn: **B.AINSWORTH/A.SAVAGE/D.JENKINS**

Date: **SEP-22-92**
Copy 1. **NEW CANAMIN RESOURCES, N.VANCOUVER, B**
2. **AINSWORTH-JENKINS C/O MIN-EN SMITHERS**

We hereby certify the following Assay of 24 CORE samples submitted SEP-15-92 by DAVE JENKINS.

Sample Number	Cu %
15062	.880
15063	1.050
15064	1.120
15065	.759
15066	.341
15067	.406
15068	.353
15069	.500
15070	.166
15071	.130
15072	.110
15101	.668
15102	.453
15103	.702
15104	.990
15105	1.030
15106	1.740
15107	.658
15108	.548
15109	.655
15110	.636
15111	.930
15112	1.540
15113	1.560

Certified by 

MIN-EN LABORATORIES

II-21



MIN-EN LABORATORIES
 (DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
 CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
 705 WEST 15TH STREET
 NORTH VANCOUVER, B.C. CANADA V7M 1T2
 TELEPHONE (604) 980-5814 OR (604) 988-4524
 FAX (604) 980-9621

SMITHERS LAB.:
 3176 TATLOW ROAD
 SMITHERS, B.C. CANADA V0J 2N0
 TELEPHONE (604) 847-3004
 FAX (604) 847-3005

Assay Certificate

2S-0327-RA1

Company: **NEW CANAMIN RESOURCES**
 Project: **HUCKLEBERRY**
 Attn: **D.JENKINS/B.AINSWORTH/A.SAVAGE**

Date: **SEP-24-92**
 Copy 1. **NEW CANAMIN RESOURCES, VANCOUVER, B.C.**
 2. **AINSWORTH JENKINS, c/o MIN-EN, SMITHERS**

We hereby certify the following Assay of 24 CORE samples submitted SEP-17-92 by D. JENKINS.

Sample Number	Cu %
15120	.490
15121	.418
15122	.275
15123	.272
15124	.273
15125	.388
15126	.479
15127	.388
15128	.421
15129	.396
15130	.375
15151	.801
15152	.665
15153	.716
15154	1.330
15155	.469
15156	.794
15157	.478
15158	.248
15159	.414
15160	.870
15161	.718
15162	.646
15163	.789

Certified by 

MIN-EN LABORATORIES

II-23



**MIN
EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:

705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:

3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

2S-0327-RA2

Company: **NEW CANAMIN RESOURCES**
Project: **HUCKLEBERRY**
Attn: **D.JENKINS/B.AINSWORTH/A.SAVAGE**

Date: **SEP-24-92**

Copy 1. **NEW CANAMIN RESOURCES, VANCOUVER, B.C.**
2. **AINSWORTH JENKINS, c/o MIN-EN, SMITHERS**

We hereby certify the following Assay of 24 CORE samples
submitted SEP-17-92 by D. JENKINS.

Sample Number	Cu %
15164	.619
15165	.420
15166	.601
15167	.220
15168	.388
15169	.253
15170	.632
15171	.267
15172	.182
15173	.411
15174	.218
15175	.309
15176	.321
15177	.305
15178	.326
15201	.132
15202	.576
15203	.505
15204	.225
15205	.281
15206	.666
15207	.585
15208	.602
15209	.684

Certified by _____

MIN-EN LABORATORIES

II-24



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:
3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

2S-0327-RA3

Company: **NEW CANAMIN RESOURCES**
Project: **HUCKLEBERRY**
Attn: **D.JENKINS/B.AINSWORTH/A.SAVAGE**

Date: **SEP-24-92**
Copy 1. **NEW CANAMIN RESOURCES, VANCOUVER, B.C.**
2. **AINSWORTH JENKINS, c/o MIN-EN, SMITHERS**

We hereby certify the following Assay of 24 CORE samples submitted SEP-17-92 by D. JENKINS.

Sample Number	Cu %
15210	.653
15211	.480
15212	1.170
15213	.727
15214	1.190
15215	.233
15216	.613
15217	.708
15218	.454
15219	.474
15220	.980
15221	.576
15222	.960
15223	.479
15224	.771
15225	.421
15226	.363
15227	.404
15228	.760
15229	.668
15230	.890
15231	1.020
15232	.626
15233	.940

Certified by _____

MIN-EN LABORATORIES

II - 25



MIN-EN LABORATORIES
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:
3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

2S-0327-RA4

Company: **NEW CANAMIN RESOURCES**
Project: **HUCKLEBERRY**
Attn: **D.JENKINS/B.AINSWORTH/A.SAVAGE**

Date: **SEP-24-92**
Copy 1. **NEW CANAMIN RESOURCES, VANCOUVER, B.C.**
2. **AINSWORTH JENKINS, c/o MIN-EN, SMITHERS**

We hereby certify the following Assay of 24 CORE samples submitted SEP-17-92 by D. JENKINS.

Sample Number	Cu %
15234	.548
15235	.431
15236	.516
15237	.669
15238	.535
15239	.524
15240	.715
15241	1.080
15242	.910
15243	.691
15244	.412
15245	.520
15246	.440
15247	.473
15248	.235
15251	.652
15252	.576
15253	.730
15254	.622
15255	.311
15256	.285
15257	.424
15258	.236
15259	.282

Certified by 

MIN-EN LABORATORIES

II-20



MIN-EN LABORATORIES
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:

705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:

3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

2S-0327-RA5

Company: **NEW CANAMIN RESOURCES**
Project: **HUCKLEBERRY**
Attn: **D.JENKINS/B.AINSWORTH/A.SAVAGE**

• Date: **SEP-24-92**

Copy 1. **NEW CANAMIN RESOURCES, VANCOUVER, B.C.**
2. **AINSWORTH JENKINS, c/o MIN-EN, SMITHERS**

We hereby certify the following Assay of 2 CORE samples submitted SEP-17-92 by D. JENKINS.

Sample Number	Cu %
15261	.405
15262	.489

Certified by _____

MIN-EN LABORATORIES

II-27



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:
3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

2S-0330-RA2

Company: **NEW CANAMIN RESOURCES**
Project: **HUCKLEBERRY**
Attn: **B.AINSWORTH/A.SAVAGE/D.JENKINS**

Date: **SEP-25-92**
Copy 1. **NEW CANAMIN RESOURCES, VANCOUVER, B.C.**
2. **AINSWORTH JENKINS, c/o MIN-EN SMITHERS**

We hereby certify the following Assay of 1 CORE samples submitted SEP-20-92 by D. JENKINS.

Sample Number	Cu %
15287	.137

Certified by 

MIN-EN LABORATORIES



MIN-EN LABORATORIES
 (DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
 CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
 705 WEST 15TH STREET
 NORTH VANCOUVER, B.C. CANADA V7M 1T2
 TELEPHONE (604) 980-5814 OR (604) 988-4524
 FAX (604) 980-9621

SMITHERS LAB.:
 3176 TATLOW ROAD
 SMITHERS, B.C. CANADA V0J 2N0
 TELEPHONE (604) 847-3004
 FAX (604) 847-3005

Assay Certificate

2S-0332-RA1

Company: **NEW CANAMIN RESOURCES**
 Project: **HUCKLEBERRY**
 Attn: **B.AINSWORTH/A.SAVAGE**

Date: **SEP-25-92**

Copy 1. **NEW CANAMIN RESOURCES, N.VANCOUVER, B**
 2. **AINSWORTH-JENKINS C/O MIN-EN SMITHERS**

We hereby certify the following Assay of 24 CORE samples submitted SEP-21-92 by DAVID JENKINS.

Sample Number	Cu %
15321	.157
15322	.150
15323	.167
15324	.191
15325	.181
15326	.164
15327	.227
15328	.448
15329	.275
15330	.318
15331	.230
15332	.246
15333	.229
15334	.203
15335	.289
15336	.235
15337	.384
15351	.338
15352	.356
15353	.439
15354	.382
15355	.366
15356	.383
15357	.328

Certified by 

MIN-EN LABORATORIES



MIN-EN LABORATORIES
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:
3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

2S-0332-RA2

Company: **NEW CANAMIN RESOURCES**
Project: **HUCKLEBERRY**
Attn: **B.AINSWORTH/A.SAVAGE**

Date: **SEP-25-92**

- Copy 1. NEW CANAMIN RESOURCES, N.VANCOUVER, B
2. AINSWORTH-JENKINS C/O MIN-EN SMITHERS

We hereby certify the following Assay of 21 CORE samples submitted SEP-21-92 by DAVID JENKINS.

Sample Number	Cu %
15358	.164
15359	.417
15360	.212
15361	.147
15362	.354
15363	.216
15364	.365
15365	.186
15366	.481
15367	.472
15368	.242
15369	.540
15370	.361
15371	.296
15372	.319
15373	.297
15374	.333
15375	.358
15376	.283
15377	.326
15378	.344

Certified by _____

MIN-EN LABORATORIES

II-32



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:
3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

2S-0334-RA1

Company: **NEW CANAMIN RESOURCES**
Project: **HUCKLEBERRY**
Attn: **B.AINSWORTH/A.SAVAGE/D.JENKINS**

Date: **SEP-25-92**
Copy 1. **NEW CANAMIN RESOURCES, VANCOUVER, B.C.**
2. **AINSWORTH JENKINS, c/o MIN-EN SMITHERS**

We hereby certify the following Assay of 24 CORE samples submitted SEP-21-92 by D. JENKINS.

Sample Number	Cu %
15401	.107
15402	.395
15403	.417
15404	.434
15405	.386
15406	.359
15407	.522
15408	.829
15409	.625
15410	.551
15411	.788
15412	.910
15413	1.200
15414	.591
15415	.612
15416	.675
15417	.538
15418	.386
15419	.740
15420	.574
15421	.491
15422	.620
15423	1.500
15424	.695

Certified by 

MIN-EN LABORATORIES



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:
3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

2S-0334-RA2

Company: **NEW CANAMIN RESOURCES**
Project: **HUCKLEBERRY**
Attn: **B.AINSWORTH/A.SAVAGE/D.JENKINS**

Date: **SEP-25-92**
Copy 1. **NEW CANAMIN RESOURCES, VANCOUVER, B.C.**
2. **AINSWORTH JENKINS, c/o MIN-EN SMITHERS**

We hereby certify the following Assay of 9 CORE samples submitted SEP-21-92 by D. JENKINS.

Sample Number	Cu %
15425	1.080
15426	1.150
15427	.804
15428	.719
15429	.825
15430	.621
15431	.303
15432	.398
15433	.446

Certified by 

MIN-EN LABORATORIES

II-34



**MIN-EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:
3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

2S-0339-RA1

Company: **NEW CANAMIN RESOURCES**
Project: **HUCKELBERRY**
Attn: **B AINSWORTH/A SAVAGE/D JENKINS**

Date: **OCT-01-92**
Copy 1. **NEW CANAMIN RESOURCES, VANCOUVER, B.C.**

We hereby certify the following Assay of 24 CORE samples submitted SEP-28-92 by D. JENKINS.

Sample Number	Cu %
1-15451	.524
1-15452	.511
1-15453	1.080
1-15454	1.070
1-15455	.519
1-15456	.510
1-15457	.700
1-15458	.727
1-15459	.371
1-15460	.747
1-15461	.523
1-15462	.610
1-15463	.573
1-15464	.289
1-15465	.422
1-15466	.255
1-15467	.311
1-15468	.275
1-15469	.284
1-15470	.305
1-15471	.312
1-15472	.517
1-15473	.325
1-15474	.483

Certified by _____

MIN-EN LABORATORIES

11-36



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:

705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:

3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

2S-0339-RA2

Company: **NEW CANAMIN RESOURCES**
Project: **HUCKELBERRY**
Attn: **B AINSWORTH/A SAVAGE/D JENKINS**

Date: **OCT-01-92**

Copy 1. NEW CANAMIN RESOURCES, VANCOUVER, B.C.

We hereby certify the following Assay of 4 CORE samples
submitted SEP-28-92 by D. JENKINS.

Sample Number	Cu %
1-15475	.231
1-15476	.371
1-15477	.131
1-15478	.142

Certified by _____

MIN-EN LABORATORIES

II-37



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:
3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate


2S-0340-RA1

Company: **NEW CANAMIN RESOURCES**
Project: **HUCKELBERRY**
Attn: **B AINSWORTH/A SAVAGE/D JENKINS**

Date: **OCT-02-92**
Copy 1. NEW CANAMIN RESOURCES, VANCOUVER, B.C.

We hereby certify the following Assay of 24 CORE samples submitted SEP-28-92 by D. JENKINS.

Sample Number	Cu %
1-15501	.229
1-15502	.296
1-15503	.386
1-15504	.498
1-15505	.251
1-15506	.306
1-15507	.340
1-15508	.180
1-15509	.289
1-15510	.207
1-15511	.181
1-15512	.218
1-15513	.158
1-15514	.175
1-15515	.248
1-15516	.311
1-15517	.506
1-15518	.547
1-15519	.262
1-15520	.158
1-15521	.372
1-15522	.275
1-15523	.266
1-15524	.333

Certified by 

MIN-EN LABORATORIES

II-38



**MIN
EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:

705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:

3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

2S-0340-RA2

Company: **NEW CANAMIN RESOURCES**
Project: **HUCKELBERRY**
Attn: **B AINSWORTH/A SAVAGE/D JENKINS**

Date: **OCT-02-92**

Copy 1. NEW CANAMIN RESOURCES, VANCOUVER, B.C.

We hereby certify the following Assay of 13 CORE samples submitted SEP-28-92 by D. JENKINS.

Sample Number	Cu %
1-15525	.210
1-15526	.337
1-15527	.247
1-15528	.162
1-15529	.155
1-15530	.302
1-15531	.207
1-15532	.076
1-15533	.218
1-15534	.129
1-15535	.147
1-15536	.077
1-15537	.077

Certified by _____

MIN-EN LABORATORIES



MIN-EN LABORATORIES
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:
3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

2S-0341-RA1

Company: **NEW CANAMIN RESOURCES**
Project: **HUCKELBERRY**
Attn: **B AINSWORTH/A SAVAGE/D JENKINS**

Date: **OCT-02-92**
Copy 1. **NEW CANAMIN RESOURCES, VANCOUVER, B.C.**

We hereby certify the following Assay of 24 CORE samples submitted SEP-28-92 by D. JENKINS.

Sample Number	Cu %
1-15551	.311
1-15552	.561
1-15553	.296
1-15554	.293
1-15555	.160
1-15556	.265
1-15557	.539
1-15558	.329
1-15559	.390
1-15560	.484
1-15561	.263
1-15562	.285
1-15563	.377
1-15564	.267
1-15565	.382
1-15566	.459
1-15567	.524
1-15568	.356
1-15569	.260
1-15570	.220
1-15571	.370
1-15572	.615
1-15573	.312
1-15574	.813

Certified by _____

MIN-EN LABORATORIES

II - 40



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:
3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

2S-0341-RA2

Company: **NEW CANAMIN RESOURCES**
Project: **HUCKELBERRY**
Attn: **B AINSWORTH/A SAVAGE/D JENKINS**

Date: **OCT-01-92**
Copy 1. **NEW CANAMIN RESOURCES, VANCOUVER, B.C.**

We hereby certify the following Assay of 14 CORE samples submitted SEP-28-92 by D. JENKINS.

Sample Number	Cu %
1-15575	.920
1-15576	.741
1-15577	.252
1-15578	.233
1-15579	.317
1-15580	.512
1-15581	.329
1-15582	.309
1-15583	.335
1-15584	.418
1-15585	.396
1-15586	.184
1-15587	.502
1-15588	.008

Certified by 

MIN-EN LABORATORIES

II - 41



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:
3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

2S-0342-RA1

Company: **NEW CANAMIN RESOURCES**
Project: **HUCKELBERRY**
Attn: **B AINSWORTH/A SAVAGE/D JENKINS**

Date: **OCT-02-92**
Copy 1. **NEW CANAMIN RESOURCES, VANCOUVER, B.C.**

We hereby certify the following Assay of 11 CORE samples submitted SEP-28-92 by DAVE JENKINS.

Sample Number	Cu %
1-15601	.258
1-15602	.441
1-15603	.464
1-15604	.263
1-15605	.353
1-15606	.301
1-15607	.194
1-15608	.236
1-15609	.203
1-15610	.240
1-15611	.347

Certified by _____

MIN-EN LABORATORIES

II-42



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:

705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:

3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

2S-0343-RA1

Company: **NEW CANAMIN RESOURCES**
Project: **HUCKELBERRY**
Attn: **B AINSWORTH/A SAVAGE/D JENKINS**

Date: **OCT-02-92**

Copy 1. NEW CANAMIN RESOURCES, VANCOUVER, B.C.

We hereby certify the following Assay of 20 CORE samples
submitted SEP-28-92 by DAVE JENKINS.

Sample Number	Cu %
1-15651	.161
1-15652	.272
1-15653	.264
1-15654	.268
1-15655	.262
1-15656	.294
1-15657	.331
1-15658	.298
1-15659	.252
1-15660	.262
1-15661	.360
1-15662	.324
1-15663	.194
1-15664	.209
1-15665	.222
1-15666	.388
1-15667	.206
1-15668	.366
1-15669	.296
1-15670	.160

Certified by _____

MIN-EN LABORATORIES

II-43



**MIN-EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:

705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:

3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

2S-0344-RA1

Company: **NEW CANAMIN RESOURCES**
Project: **HUCKELBERRY**
Attn: **B AINSWORTH/A SAVAGE/D JENKINS**

Date: **OCT-06-92**
Copy 1. **NEW CANAMIN RESOURCES, VANCOUVER, B.C.**

We hereby certify the following Assay of 24 CORE samples submitted SEP-28-92 by DAVE JENKINS.

Sample Number	Cu %
1-15701	.458
1-15702	.361
1-15703	.191
1-15704	.172
1-15705	.167
1-15706	.161
1-15707	.107
1-15708	.092
1-15709	.093
1-15710	.162
1-15711	.362
1-15712	.235
1-15713	.199
1-15714	.535
1-15715	.618
1-15716	.363
1-15717	.440
1-15718	1.020
1-15719	.550
1-15720	.830
1-15721	.394
1-15722	.371
1-15723	.452
1-15724	.416

Certified by _____

MIN-EN LABORATORIES

II-44



MIN-EN LABORATORIES
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:
3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

2S-0344-RA2

Company: **NEW CANAMIN RESOURCES**
Project: **HUCKELBERRY**
Attn: **B AINSWORTH/A SAVAGE/D JENKINS**

Date: **OCT-06-92**
Copy 1. NEW CANAMIN RESOURCES, VANCOUVER, B.C.

We hereby certify the following Assay of 3 CORE samples submitted SEP-28-92 by DAVE JENKINS.

Sample Number	Cu %
1-15725	.543
1-15726	.327
1-15727	.454

Certified by _____

MIN-EN LABORATORIES

II - 45



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:
3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate


2V-1103-RA1

Company: **NEW CANAMIN RESOURCES**
Project:
Attn: **B AINSWORTH/A SAVAGE/D JENKINS**

Date: **OCT-02-92**
Copy 1. NEW CANAMIN RESOURCES, VANCOUVER, B.C.

We hereby certify the following Assay of 14 CORE samples submitted OCT-01-92 by DAVE JENKINS.

Sample Number	Cu %
15728	.389
15729	.294
15730	.207
15731	.291
15732	.355
15733	.189
15734	.382
15735	.263
15736	.296
15737	.355
15738	.352
15739	.476
15740	.474
15741	.314

Certified by 
MIN-EN LABORATORIES

II - 46



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:
3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

2S-0361-RA1

Company: **NEW CANAMIN RESOURCES**
Project: **HUCKLEBERRY**
Attn: **B.AINSWORTH/A.SAVAGE/D.JENKINS**

Date: **OCT-15-92**
Copy 1. NEW CANAMIN RESOURCES, NORTH VANCOUV

We hereby certify the following Assay of 24 CORE samples submitted OCT-13-92 by D.JENKINS.

Sample Number	Cu %
15751	.636
15752	1.120
15753	1.000
15754	.920
15755	1.670
15756	.802
15757	.595
15758	.706
15759	.647
15760	.900
15761	1.110
15762	.284
15763	.393
15764	.563
15765	.634
15766	.472
15767	.391
15768	.417
15769	.408
15770	.805
15771	.562
15772	.675
15773	.736
15774	.574

Certified by 

MIN-EN LABORATORIES

II - 47



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:

705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:

3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

2S-0361-RA2

Company: **NEW CANAMIN RESOURCES**
Project: **HUCKLEBERRY**
Attn: **B.AINSWORTH/A.SAVAGE/D.JENKINS**

Date: **OCT-15-92**
Copy 1. NEW CANAMIN RESOURCES, NORTH VANCOUV

We hereby certify the following Assay of 12 CORE samples submitted OCT-13-92 by D.JENKINS.

Sample Number	Cu %
15775	.576
15776	.464
15777	.618
15778	.295
15779	.631
15780	.601
15781	.900
15782	.910
15783	.639
15784	.665
15785	.870
15786	.762

Certified by _____

MIN-EN LABORATORIES

II - 48



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:

705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:

3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

2S-0362-RA1

Company: **NEW CANAMIN RESOURCES**
Project: **HUCKELBERRY**
Attn: **B AINSWORTH/A SAVAGE/D JENKINS**

Date: **OCT-20-92**
Copy 1. **NEW CANAMIN RESOURCES, VANCOUVER, B.C.**
2. **DAVE JENKINS, c/o MIN-EN LABS SMITHERS**

We hereby certify the following Assay of 24 CORE samples
submitted OCT-15-92 by DAVE JENKINS.

Sample Number	Cu %
15801	.860
15802	.700
15803	.870
15804	.950
15805	.940
15806	.311
15807	.666
15808	.413
15809	1.040
15810	.519
15811	.311
15812	.271
15813	.260
15814	.233
15815	.297
15816	.353
15817	.614
15818	.785
15819	.340
15820	.351
15821	.483
15822	.350
15823	.418
15824	.709

Certified by _____

MIN-EN LABORATORIES

II - 49



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:
3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

2S-0362-RA2

Company: **NEW CANAMIN RESOURCES**
Project: **HUCKELBERRY**
Attn: **B AINSWORTH/A SAVAGE/D JENKINS**

Date: **OCT-20-92**
Copy 1. **NEW CANAMIN RESOURCES, VANCOUVER, B.C.**
2. **DAVE JENKINS, c/o MIN-EN LABS SMITHERS**

We hereby certify the following Assay of 16 CORE samples submitted OCT-15-92 by DAVE JENKINS.

Sample Number	Cu %
15825	.440
15826	.335
15827	.437
15828	.258
15829	.286
15830	.642
15831	.490
15832	.756
15833	.795
15834	.850
15835	.880
15836	.676
15837	.596
15838	1.480
15839	.564
15840	.851

Certified by _____

MIN-EN LABORATORIES

II - 500



**MINERAL
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:

705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:

3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

2S-0365-RA1

Company: **NEW CANAMIN RESOURCES**
Project: **HUCKLEBERRY**
Attn: **B.AINSWORTH/A.SAVAGE/D.JENKINS**

Date: **OCT-23-92**
Copy 1. **NEW CANAMIN RESOURCES, NORTH VANCOUV**
2. **DAVE JENKINS, C/O MIN-EN LABS SMITHERS**

We hereby certify the following Assay of 17 CORE samples submitted OCT-21-92 by DAVE JENKINS.

Sample Number	Cu %
15094	.345
15095	.743
15096	.449
15097	.336
15098	.262
15099	.582
15100	.451
15841	.434
15842	.563
15843	.753
15844	.564
15845	1.120
15846	.910
15847	.854
15848	.631
15849	.337
15850	.545

Certified by _____

MIN-EN LABORATORIES

II-51



MIN-EN LABORATORIES
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:
3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

2S-0366-RA1

Company: **NEW CANAMIN RESOURCES**
Project: **HUCKLEBERRY**
Attn: **B.AINSWORTH/A.SAVAGE/D.JENKINS**

Date: **OCT-23-92**
Copy 1. **NEW CANAMIN RESOURCES, NORTH VANCOUV**
2. **DAVE JENKINS, C/O MIN-EN LABS SMITHERS**

We hereby certify the following Assay of 24 CORE samples submitted OCT-21-92 by DAVE JENKINS.

Sample Number	Cu %
15851	.309
15852	.447
15853	.526
15854	.440
15855	.386
15856	.639
15857	.440
15858	.190
15859	.157
15860	.291
15861	.414
15862	.174
15863	.132
15864	.208
15865	.140
15866	.253
15867	.412
15868	.347
15869	.198
15870	.379
15871	.373
15872	.274
15873	.214
15874	.441

Certified by _____

MIN-EN LABORATORIES

II-52



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:
3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

2S-0366-RA2

Company: **NEW CANAMIN RESOURCES**
Project: **HUCKLEBERRY**
Attn: **B.AINSWORTH/A.SAVAGE/D.JENKINS**

Date: **OCT-27-92**
Copy 1. **NEW CANAMIN RESOURCES, VANCOUVER, B.C.**
2. **DAVE JENKINS, C/O MIN-EN LABS SMITHERS**

We hereby certify the following Assay of 24 CORE samples submitted OCT-21-92 by DAVE JENKINS.

Sample Number	Cu %
15875	.511
15876	.695
15877	.634
15878	.548
15879	.435
15880	.372
15881	.325
15882	.245
15883	.197
15884	.325
15885	.299
15886	.307
15887	.341
15888	.212
15889	.359
15890	.308
15891	.229
15892	.179
15893	.415
15894	.540
15895	.447
15896	1.120
15897	.371
15898	.525

Certified by 

MIN-EN LABORATORIES



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:

705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:

3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

2S-0366-RA3

Company: **NEW CANAMIN RESOURCES**
Project: **HUCKLEBERRY**
Attn: **B.AINSWORTH/A.SAVAGE/D.JENKINS**

Date: **OCT-27-92**

Copy 1. **NEW CANAMIN RESOURCES, VANCOUVER, B.C.**
2. **DAVE JENKINS, C/O MIN-EN LABS SMITHERS**

We hereby certify the following Assay of 2 CORE samples
submitted OCT-21-92 by DAVE JENKINS.

Sample Number	Cu %
15899	.479
15900	.255

Certified by _____

MIN-EN LABORATORIES

II-5-4



MIN-EN LABORATORIES
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:
3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate


2S-0367-RA1

Company: **NEW CANAMIN RESOURCES**
Project: **HUCKELBERRY**
Attn: **B. AINSWORTH/B. SAVAGE**

Date: **OCT-26-92**
Copy 1. **NEW CANAMIN RESOURCES, VANCOUVER, B.C.**
2. **DAVE JENKINS, c/o MIN-EN SMITHERS, B.C.**

We hereby certify the following Assay of 24 CORE samples submitted OCT-21-92 by DAVE JENKINS.

Sample Number	Cu %
15901	.280
15902	.387
15903	.558
15904	.748
15905	.606
15906	.380
15907	.441
15908	.313
15909	.315
15910	.232
15911	.260
15912	.323
15913	.427
15914	.401
15915	.390
15916	.356
15917	.363
15918	.980
15919	.667
15920	.563
15921	.830
15922	.731
15923	.599
15924	.679

Certified by 

MIN-EN LABORATORIES

II - 555



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:
3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

2S-0367-RA2

Company: **NEW CANAMIN RESOURCES**
Project: **HUCKELBERRY**
Attn: **B. AINSWORTH/B. SAVAGE**

Date: **OCT-26-92**

Copy 1. **NEW CANAMIN RESOURCES, VANCOUVER, B.C.**
2. **DAVE JENKINS, c/o MIN-EN SMITHERS, B.C.**

We hereby certify the following Assay of 20 CORE samples submitted OCT-21-92 by DAVE JENKINS.

Sample Number	Cu %
15925	.588
15926	.219
15927	.249
15928	.367
15929	.469
15930	.371
15931	.356
15932	.331
15933	.198
15934	.264
15935	.229
15936	.224
15937	.175
15938	.238
15939	.120
15940	.276
15941	.188
15942	.349
15943	.230
15944	.239

Certified by _____ 

MIN-EN LABORATORIES

II-576



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:
3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

2S-0368-RA2

Company: **NEW CANAMIN RESOURCES**
Project: **HUCKLEBERRY**
Attn: **B.AINSWORTH/A.SAVAGE/D.JENKINS**

Date: **OCT-27-92**
Copy 1. **NEW CANAMIN RESOURCES, VANCOUVER, B.C.**
2. **DAVE JENKINS, C/O MIN-EN LABS SMITHERS**

We hereby certify the following Assay of 15 CORE samples submitted OCT-21-92 by DAVE JENKINS.

Sample Number	CJ %
15977	1.000
15978	.816
15979	.751
15980	1.590
15981	.970
15982	.735
15983	.435
15984	.400
15985	.394
15986	.327
15987	.435
15988	.290
15989	.337
15990	.235
15991	.118

Certified by _____

MIN-EN LABORATORIES

II - 578



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:

705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:

3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

2S-0369-RA1

Company: **NEW CANAMIN RESOURCES**
Project: **HUCKELBERRY**
Attn: **B. AINSWORTH/A. SAVAGE**

Date: **OCT-27-92**

We hereby certify the following Assay of 24 CORE samples
submitted OCT-21-92 by D. JENKINS.

Sample Number	CU %
17001	.290
17002	.385
17003	.453
17004	.613
17005	.480
17006	.262
17007	.447
17008	.599
17009	.225
17010	.609
17011	.574
17012	.356
17013	.466
17014	.428
17015	.446
17016	.364
17017	.470
17018	.554
17019	.526
17020	.475
17021	.272
17022	.318
17023	.380
17024	.396

Certified by _____

MIN-EN LABORATORIES

II - 5 - 9



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:

705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:

3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

2S-0369-RA2

Company: **NEW CANAMIN RESOURCES**
Project: **HUCKELBERRY**
Attn: **B. AINSWORTH/A. SAVAGE**

Date: **OCT-27-92**

We hereby certify the following Assay of 1 CORE samples
submitted OCT-21-92 by D. JENKINS.

Sample Number	Cu %
17025	.479

Certified by _____

MIN-EN LABORATORIES

II - 60



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:
3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

2S-0372-RA1

Company: **NEW CANAMIN RESOURCES**
Project: **HUCKLEBERRY**
Attn: **B.AINSWORTH/A.SAVAGE/D.JENKINS**

Date: **OCT-27-92**
Copy 1. **NEW CANAMIN RESOURCES, VANCOUVER, B.C.**
2. **DAVE JENKINS, C/O MIN-EN LABS SMITHERS**

We hereby certify the following Assay of 6 CORE samples submitted OCT-23-92 by DAVE JENKINS.

Sample Number	Cu %
17051	.241
17052	.354
17053	.129
17054	.218
17055	.514
17056	.427

Certified by _____

MIN-EN LABORATORIES

II - 61



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:

705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:

3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

2S-0374-RA2

Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attn: **B.AINSWORTH/A.SAVAGE/D.JENKINS**

Date: **NOV-05-92**

Copy 1. **NEW CANAMIN RESOURCES, NORTH VANCOUVER**
2. **AINSWORTH-JENKINS, VANCOUVER, B.C.**

We hereby certify the following Assay of 24 CORE samples submitted OCT-30-92 by DAVE JENKINS.

Sample Number	Cu %
17078	.227
17079	.179
17080	.371
17081	.341
17082	.392
17083	.387
17084	.356
17085	.540
17086	.723
17087	.582
17088	.715
17089	.718
17090	.577
17091	.657
17092	.629
17093	.980
17094	.557
17095	.461
17096	.533
17097	.391
17098	.438
17099	.378
17100	.363
17101	.301

Certified by _____

MIN-EN LABORATORIES

II - 63



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:
3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

2S-0374-RA3

Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attn: **B.AINSWORTH/A.SAVAGE/D.JENKINS**

Date: **NOV-05-92**
Copy 1. **NEW CANAMIN RESOURCES, NORTH VANCOUVER**
2. **AINSWORTH-JENKINS, VANCOUVER, B.C.**

We hereby certify the following Assay of 24 CORE samples submitted OCT-30-92 by DAVE JENKINS.

Sample Number	Cu %
17102	.176
17103	.084
17104	.171
17105	.163
17106	.230
17107	.990
17108	.293
17109	.418
17110	.509
17111	.453
17112	.350
17113	.400
17114	.370
17115	.247
17116	.291
17117	.242
17118	.382
17119	.346
17120	.514
17121	.332
17122	.198
17123	.212
17124	.422
17125	.291

Certified by _____ 

MIN-EN LABORATORIES

II-64



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:

705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:

3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

2S-0374-RA4

Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attn: **B.AINSWORTH/A.SAVAGE/D.JENKINS**

Date: **NOV-05-92**

Copy 1. **NEW CANAMIN RESOURCES, NORTH VANCOUVER**
2. **AINSWORTH-JENKINS, VANCOUVER, B.C.**

We hereby certify the following Assay of 24 CORE samples submitted OCT-30-92 by DAVE JENKINS.

Sample Number	Cu %
17126	.372
17127	.249
17128	.232
17129	.271
17130	.380
17131	.412
17132	.471
17133	.533
17134	.439
17135	.331
17136	.275
17137	.308
17138	.387
17139	.338
17140	.630
17141	1.050
17151	.137
17152	.154
17153	.159
17154	.350
17155	.181
17156	.162
17157	.146
17158	.277

Certified by _____

MIN-EN LABORATORIES

II - 65 -



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:

705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:

3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

2S-0374-RA5

Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attn: **B.AINSWORTH/A.SAVAGE/D.JENKINS**

Date: **NOV-05-92**
Copy 1. **NEW CANAMIN RESOURCES, NORTH VANCOUVER**
2. **AINSWORTH-JENKINS, VANCOUVER, B.C.**

We hereby certify the following Assay of 24 CORE samples submitted OCT-30-92 by DAVE JENKINS.

Sample Number	Cu %
17159	.251
17160	.259
17161	.150
17162	.144
17163	.166
17164	.150
17165	.227
17166	.185
17167	.259
17168	.277
17169	.376
17170	.247
17171	.323
17172	.386
17173	.369
17174	.375
17175	.266
17176	.232
17177	.224
17178	.500
17179	.440
17201	1.070
17202	.311
17203	.355

Certified by _____

MIN-EN LABORATORIES

II - 66



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:
3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

2S-0374-RA6

Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attn: **B.AINSWORTH/A.SAVAGE/D.JENKINS**

Date: **NOV-05-92**

Copy 1. **NEW CANAMIN RESOURCES, NORTH VANCOUVER**
2. **AINSWORTH-JENKINS, VANCOUVER, B.C.**

We hereby certify the following Assay of 24 CORE samples submitted OCT-30-92 by DAVE JENKINS.

Sample Number	Cu %
17204	.382
17205	.289
17206	.428
17207	.845
17208	.587
17209	.513
17210	.850
17211	.727
17212	.455
17213	.213
17214	.211
17215	.159
17216	.232
17217	.373
17218	.605
17219	.570
17220	.710
17221	.910
17222	.640
17223	.419
17224	.364
17225	.870
17226	.637
17227	.666

Certified by _____ 

MIN-EN LABORATORIES

II - 67



MIN-EN LABORATORIES
 (DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
 CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
 705 WEST 15TH STREET
 NORTH VANCOUVER, B.C. CANADA V7M 1T2
 TELEPHONE (604) 980-5814 OR (604) 988-4524
 FAX (604) 980-9621

SMITHERS LAB.:
 3176 TATLOW ROAD
 SMITHERS, B.C. CANADA V0J 2N0
 TELEPHONE (604) 847-3004
 FAX (604) 847-3005

Assay Certificate

2S-0374-RA7

Company: **NEW CANAMIN RESOURCES LTD.**
 Project: **HUCKLEBERRY**
 Attn: **B.AINSWORTH/A.SAVAGE/D.JENKINS**

Date: **NOV-05-92**

Copy 1. **NEW CANAMIN RESOURCES, NORTH VANCOUV**
 2. **AINSWORTH-JENKINS, VANCOUVER, B.C.**

We hereby certify the following Assay of 8 CORE samples submitted OCT-30-92 by DAVE JENKINS.

Sample Number	Cu %
17228	.415
17229	.250
17230	.332
17231	.186
17232	.150
17233	.230
17234	.294
17235	

Certified by _____

MIN-EN LABORATORIES

II-69



**MIN
EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:

705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:

3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

2S-0379-RA1

Company: **NEW CANAMIN RESOURCES**
Project: **HUCKELBERRY**
Attn: **B.AINSWORTH/A.SAVAGE/D.JENKINS**

Date: **NOV-13-92**
Copy 1. **NEW CANAMIN RESOURCES, N.VANCOUVER, B**
2. **AINSWORTH-JENKINS, VANCOUVER, B.C.**

We hereby certify the following Assay of 24 CORE samples
submitted NOV-03-92 by D. JENKINS.

Sample Number	CU %
17251	.293
17252	.399
17253	.385
17254	.588
17255	.238
17256	.339
17257	.187
17258	.154
17259	.289
17260	.185
17261	.454
17262	.325
17264	.414
17265	.560
17266	.286
17267	.344
17268	.145
17269	.256
17270	.506
17271	.531
17272	.529
17273	.577
17274	.473
17275	.467

Certified by _____

MIN-EN LABORATORIES

II-69



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:
3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

2S-0379-RA2

Company: **NEW CANAMIN RESOURCES**
Project: **HUCKELBERRY**
Attn: **B.AINSWORTH/A.SAVAGE/D.JENKINS**

Date: **NOV-16-92**
Copy 1. **NEW CANAMIN RESOURCES, N.VANCOUVER, B**
2. **AINSWORTH-JENKINS, VANCOUVER, B.C.**

We hereby certify the following Assay of 24 CORE samples submitted NOV-03-92 by D. JENKINS.

Sample Number	Cu %
17276	.383
17277	.482
17278	.380
17279	.460
17280	.350
17281	.367
17282	.508
17283	.415
17284	.321
17285	.229
17286	.314
17287	.190
17288	.114
17289	.294
17290	.232
17291	.455
17292	.413
17293	.256
17294	.381
17295	.346
17296	.332
17297	.254
17801	.324
17802	.283

Certified by _____

MIN-EN LABORATORIES

II - 70



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:
3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

2S-0379-RA3

Company: **NEW CANAMIN RESOURCES**
Project: **HUCKELBERRY**
Attn: **B.AINSWORTH/A.SAVAGE/D.JENKINS**

Date: **NOV-13-92**
Copy 1. **NEW CANAMIN RESOURCES, N.VANCOUVER, B**
2. **AINSWORTH-JENKINS, VANCOUVER, B.C.**

We hereby certify the following Assay of 24 CORE samples submitted NOV-03-92 by D. JENKINS.

Sample Number	Cu %
17803	.208
17804	.649
17805	.327
17806	.268
17807	.207
17808	.215
17809	.160
17810	.313
17811	.216
17812	.279
17813	.265
17814	.284
17815	.257
17816	.313
17817	.328
17818	.308
17819	.843
17820	.619
17821	.686
17822	1.050
17823	1.060
17824	1.340
17825	.642
17826	1.310

Certified by 

MIN-EN LABORATORIES

II - 31



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:

705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:

3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

2S-0379-RA4

Company: **NEW CANAMIN RESOURCES**
Project: **HUCKELBERRY**
Attn: **B.AINSWORTH/A.SAVAGE/D.JENKINS**

Date: **NOV-13-92**
Copy 1. **NEW CANAMIN RESOURCES, N.VANCOUVER, B**
2. **AINSWORTH-JENKINS, VANCOUVER, B.C.**

We hereby certify the following Assay of 22 CORE samples submitted NOV-03-92 by D. JENKINS.

Sample Number	Cu %
17827	1.060
17828	.743
17829	.758
17830	.544
17831	.137
17832	.467
17833	.716
17834	.458
17835	.623
17836	.334
17837	.292
17838	.491
17839	.513
17840	.354
17841	.451
17842	.284
17843	.591
17844	.255
17845	.226
17846	.319
17847	.389
17848	.006

Certified by 

MIN-EN LABORATORIES

II - 72



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:
3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

3S-0021-RA1

Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attn: **B AINSWORTH/A SAVAGE/D JENKINS**

Date: **FEB-25-93**

Copy 1. **NEW CANAMIN RES. LTD., VANCOUVER, B.C.**
2. **DAVE JENKINS C/O MIN-EN SMITHERS, B.C.**


We hereby certify the following Assay of 24 CORE samples submitted FEB-16-93 by D. JENKINS.

Sample Number	Cu %
40401	.253
40402	.182
40403	.194
40404	.377
40405	.251
40406	.214
40407	.315
40408	.236
40409	.270
40410	.179
40411	.265
40412	.305
40413	.364
40414	.530
40415	.526
40416	.297
40417	.364
40418	.054
40419	.226
40420	.220
40421	.260
40422	.257
40423	.230
40424	.144

Certified by _____ 

MIN-EN LABORATORIES

II - 73



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:

705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:

3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

3S-0021-RA2


Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attn: **B AINSWORTH/A SAVAGE/D JENKINS**

Date: FEB-25-93

Copy 1. NEW CANAMIN RES. LTD., VANCOUVER, B.C.
2. DAVE JENKINS C/O MIN-EN SMITHERS, B.C.

We hereby certify the following Assay of 15 CORE samples submitted FEB-16-93 by D. JENKINS.

Sample Number	Cu %
40425	.106
40426	.112
40427	.264
40428	.139
40429	.120
40430	.081
40431	.096
40432	.247
40433	.400
40434	.349
40435	.364
40436	.440
40437	.320
40438	.495
40439	.410

Certified by _____ 

MIN-EN LABORATORIES

II - 74



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:

705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:

3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

3S-0025-RA1

Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attn: **B AINSWORTH/A SAVAGE/D JENKINS**

Date: **MAR-02-93**

Copy 1. NEW CANAMIN RES. LTD., VANCOUVER, B.C.

We hereby certify the following Assay of 24 CORE samples
submitted FEB-24-93 by DAVE JENKINS.

Sample Number	CU %
40451	.307
40452	.351
40453	.513
40454	.218
40455	.138
40456	.149
40457	.261
40458	.188
40459	.090
40460	.067
40461	.054
40462	.106
40463	.124
40464	.106
40465	.073
40466	.215
40467	.110
40468	.169
40469	.098
40470	.087
40471	.127
40472	.170
40473	.080
40474	.197

Certified by _____

MIN-EN LABORATORIES

II - 75



**MIN
EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:

705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:

3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

3S-0026-RA1

Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attn: **B AINSWORTH/A SAVAGE/D JENKINS**

Date: **MAR-02-93**
Copy 1. **NEW CANAMIN RES. LTD., VANCOUVER, B.C.**

We hereby certify the following Assay of 18 CORE samples submitted FEB-24-93 by DAVE JENKINS.

Sample Number	Cu %
40501	.754
40502	.705
40503	.885
40504	.348
40505	.427
40506	.340
40507	.318
40508	.294
40509	.336
40510	.358
40511	.405
40512	.382
40513	.360
40514	.176
40515	.467
40516	.341
40517	.461
40518	.409

Certified by _____

MIN-EN LABORATORIES

II - 7C



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:

705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:

3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

3S-0003-RA1

Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attn: **B AINSWORTH/A SAVAGE/D JENKINS**

Date: **FEB-02-93**

We hereby certify the following Assay of 6 CORE samples
submitted JAN-25-93 by D. JENKINS.

Sample Number	Cu %
17301	.457
17302	.557
17303	.436
17304	.194
17305	.465
17308	.594

Certified by _____

MIN-EN LABORATORIES

II - 77



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:
3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

3S-0008-RA1

Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attn: **B AINSWORTH/A SAVAGE/D JENKINS**

Date: **FEB-03-93**

Copy 1. **NEW CANAMIN RES. LTD., VANCOUVER, B.C.**
2. **DAVE JENKINS, C/O MIN-EN SMITHERS, B.C.**

We hereby certify the following Assay of 24 CORE samples submitted JAN-28-93 by D. JENKINS.

Sample Number	Cu %
17306	.349
17307	.460
17309	.542
17310	.564
17311	.682
17312	.388
17313	.313
17314	.278
17315	.632
17316	.257
17317	.188
17318	.463
17319	.910
17320	.526
17321	.284
17322	.293
17323	.675
17324	.451
17325	.582
17326	.500
17327	.389
17328	.403
17329	.350
17330	.281

Certified by _____

MIN-EN LABORATORIES

II - 7 e



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:

705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:

3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

3S-0008-RA2

Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attn: **B AINSWORTH/A SAVAGE/D JENKINS**

Date: **FEB-03-93**

We hereby certify the following Assay of 24 CORE samples
submitted JAN-28-93 by D. JENKINS.

Sample Number	Cu %
17331	.116
17332	.168
17333	.215
17334	.294
17335	.305
17336	.501
17337	.347
17338	.234
17339	.365
17340	.895
17341	.964
17342	.331
17351	.665
17352	1.661
17353	.742
17354	.270
17355	.252
17356	.213
17357	.164
17358	.320
17359	.522
17360	.354
17361	.395
17362	.348

Certified by _____

MIN-EN LABORATORIES

II - 79



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:

705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:

3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

3S-0008-RA3

Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attn: **B AINSWORTH/A SAVAGE/D JENKINS**

Date: **FEB-03-93**

Copy 1. **NEW CANAMIN RES. LTD., VANCOUVER, B.C.**
2. **DAVE JENKINS, C/O MIN-EN SMITHERS, B.C.**

We hereby certify the following Assay of 24 CORE samples submitted JAN-28-93 by D. JENKINS.

Sample Number	Cu %
17363	.188
17364	.132
17365	.347
17366	.384
17367	.455
17368	.960
17369	1.450
17370	.411
17371	.350
17372	.618
17373	.562
17374	.394
17375	.595
17376	.545
17377	.275
17378	.840
17379	.349
17380	.458
17381	.307
17382	.352
17389	.381
17390	.345
17391	.443
17392	.312

Certified by 

MIN-EN LABORATORIES

II - 80



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:

705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:

3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

3S-0008-RA4

Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attn: **B AINSWORTH/A SAVAGE/D JENKINS**

Date: **FEB-03-93**

Copy 1. **NEW CANAMIN RES. LTD., VANCOUVER, B.C.**
2. **DAVE JENKINS, C/O MIN-EN SMITHERS, B.C.**

We hereby certify the following Assay of 8 CORE samples submitted JAN-28-93 by D. JENKINS.

Sample Number	Cu %
17393	.386
17394	.478
17395	.553
17396	.431
17397	.534
17398	.446
17399	.897
17400	.945

Certified by _____

MIN-EN LABORATORIES

II - 81



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:
3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

3S-0009-RA1

Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attn: **B AINSWORTH/A SAVAGE/D JENKINS**

Date: FEB-03-93

Copy 1. NEW CANAMIN RES. LTD., VANCOUVER, B.C.
2. DAVE JENKINS, C/O MIN-EN SMITHERS, B.C.

We hereby certify the following Assay of 9 CORE samples
submitted JAN-28-93 by D. JENKINS.

Sample Number	Cu %
17401	1.176
17402	.534
17403	.485
17404	.334
17405	.335
17406	.320
17407	.552
17408	.835
17409	.550

Certified by _____

MIN-EN LABORATORIES

IV - 82



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:

705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:

3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

3S-0004-RA1

Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attn: **B AINSWORTH/A SAVAGE/D JENKINS**

Date: **FEB-02-93**

We hereby certify the following Assay of 24 CORE samples submitted JAN-26-93 by D. JENKINS.

Sample Number	CU %
17451	.204
17452	.190
17453	.270
17454	.474
17455	.318
17456	.316
17457	.399
17458	.504
17459	.247
17460	.546
17461	.231
17462	.625
17463	.270
17464	.419
17465	.274
17466	.451
17467	.589
17468	.353
17469	.293
17470	.137
17471	.199
17472	.336
17473	.448
17474	.198

Certified by _____

MIN-EN LABORATORIES

II - 93



MIN-EN LABORATORIES
 (DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
 CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
 705 WEST 15TH STREET
 NORTH VANCOUVER, B.C. CANADA V7M 1T2
 TELEPHONE (604) 980-5814 OR (604) 988-4524
 FAX (604) 980-9621

SMITHERS LAB.:
 3176 TATLOW ROAD
 SMITHERS, B.C. CANADA V0J 2N0
 TELEPHONE (604) 847-3004
 FAX (604) 847-3005

Assay Certificate

3S-0022-RA1

Company: **NEW CANAMIN RESOURCES LTD.**
 Project: **HUCKLEBERRY**
 Attn: **BD AINSWORTH/A SAVAGE/D JENKINS**

Date: **MAR-02-93**
 Copy 1. NEW CANAMIN RES. LTD., VANCOUVER, B.C.

We hereby certify the following Assay of 24 CORE samples submitted FEB-24-93 by DAVE JENKINS.

Sample Number	Cu %
17501	.225
17502	.228
17503	.423
17504	.227
17505	.220
17506	.149
17507	.279
17508	.242
17509	.320
17510	.293
17511	.241
17512	.150
17513	.255
17514	.236
17515	.424
17516	.113
17517	.224
17518	.240
17519	.311
17520	.236
17521	.250
17522	.267
17523	.224
17524	.286

Certified by 
 MIN-EN LABORATORIES



MIN-EN
LABORATORIES
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:

705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:

3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

3S-0022-RA2


Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attn: **BD AINSWORTH/A SAVAGE/D JENKINS**

Date: **MAR-02-93**
Copy 1. **NEW CANAMIN RES. LTD., VANCOUVER, B.C.**

We hereby certify the following Assay of 24 CORE samples
submitted FEB-24-93 by DAVE JENKINS.

Sample Number	Cu %
17525	.229
17526	.418
17527	.371
17528	.450
17529	.424
17530	.474
17531	.653
17532	.621
17533	.409
17534	.359
17535	.381
17536	.194
17537	.803
17538	.225
17539	.397
17551	.396
17552	.670
17553	.417
17554	.452
17555	.443
17556	.731
17557	.756
17558	.410
17559	.326

Certified by *Richard Long*
MIN-EN LABORATORIES



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:

705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:

3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

3S-0022-RA3

Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attn: **BD AINSWORTH/A SAVAGE/D JENKINS**

Date: **MAR-02-93**
Copy 1. NEW CANAMIN RES. LTD., VANCOUVER, B.C.

We hereby certify the following Assay of 24 CORE samples submitted FEB-24-93 by DAVE JENKINS.

Sample Number	Cu %
17560	.745
17561	.482
17562	.349
17563	.649
17564	.548
17565	.549
17566	.307
17567	.460
17568	.663
17569	.326
17570	.644
17571	1.023
17572	.682
17573	.761
17574	.494
17575	.248
17576	.363
17577	.403
17578	.422
17579	.461
17580	.962
17581	.170
17582	.282
17583	.352

Certified by *David Lupp*
MIN-EN LABORATORIES

II - 88



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:

705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:

3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

3S-0022-RA4

Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attn: **BD AINSWORTH/A SAVAGE/D JENKINS**

Date: **MAR-02-93**

Copy 1. NEW CANAMIN RES. LTD., VANCOUVER, B.C.

We hereby certify the following Assay of 1 CORE samples
submitted FEB-24-93 by DAVE JENKINS.

Sample Number	Cu %
17584	.244

Certified by

MIN-EN LABORATORIES



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:

705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:

3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

3S-0023-RA1

Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attn: **B AINSWORTH/A SAVAGE/D JENKINS**

Date: **MAR-02-93**
Copy 1. **NEW CANAMIN RES. LTD., VANCOUVER, B.C.**

We hereby certify the following Assay of 24 CORE samples submitted FEB-24-93 by DAVE JENKINS.

Sample Number	Cu %
17601	.239
17602	.443
17603	.757
17604	.792
17605	.658
17606	.829
17607	.995
17608	.802
17609	1.022
17610	1.030
17611	.554
17612	.562
17613	.430
17614	.601
17615	.379
17616	.623
17617	.626
17618	.387
17619	.875
17620	.748
17621	.221
17622	.631
17623	.459
17624	.752

Certified by *David Jenks*
MIN-EN LABORATORIES

J-90



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:
3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

3S-0023-RA2

Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attn: **B AINSWORTH/A SAVAGE/D JENKINS**

Date: **MAR-02-93**
Copy 1. **NEW CANAMIN RES. LTD., VANCOUVER, B.C.**

We hereby certify the following Assay of 11 CORE samples submitted FEB-24-93 by DAVE JENKINS.

Sample Number	Cu %
17625	.738
17626	.788
17627	.517
17628	.334
17629	.596
17630	.702
17640	.602
17641	1.270
17642	.883
17643	.768
17644	1.004

Certified by 
MIN-EN LABORATORIES



MIN-EN LABORATORIES
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:

705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:

3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

3S-0015-RA1

Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attn: **B AINSWORTH/A SAVAGE/D JENKINS**

Date: FEB-23-93

Copy 1. NEW CANAMIN RES. LTD., VANCOUVER, B.C.
2. DAVE JENKINS C/O MIN-EN SMITHERS, B.C.

We hereby certify the following Assay of 24 CORE samples
submitted FEB-16-93 by D. JENKINS.

Sample Number	Cu %
17851	.256
17852	.565
17853	.338
17854	.324
17855	.434
17856	.415
17857	.722
17858	.601
17859	.307
17860	.343
17861	.122
17862	.171
17863	.106
17864	.157
17865	.121
17866	.096
17867	.102
17868	.151
17869	.104
17870	.304
17871	.478
17872	.550
17873	.254
17874	.300

Certified by _____

MIN-EN LABORATORIES

II-92



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-8621

SMITHERS LAB.:
3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

3S-0005-RA1

Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attn: **B AINSWORTH/A SAVAGE/D JENKINS**

Date: FEB-02-93

Copy 1. NEW CANAMIN RES. LTD. VANCOUVER, B.C.
2. DAVE JENKINS C/O MIN-EN SMITHERS, B.C.

We hereby certify the following Assay of 24 CORE samples submitted JAN-25-93 by D. JENKINS.

Sample Number	Cu %
18201	.332
18202	.247
18203	.616
18204	.483
18205	.337
18206	.795
18207	.384
18208	.253
18209	.282
18210	.535
18211	.212
18212	.204
18213	.161
18214	.152
18215	.293
18216	.230
18217	.160
18218	.204
18219	.278
18220	.170
18221	.259
18222	.312
18223	.311
18224	.248

Certified by 
MIN-EN LABORATORIES

II-94



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:
3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

3S-0005-RA2

Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attn: **B AINSWORTH/A SAVAGE/D JENKINS**

Date: **FEB-02-93**

Copy 1. **NEW CANAMIN RES. LTD. VANCOUVER, B.C.**
2. **DAVE JENKINS C/O MIN-EN SMITHERS, B.C.**

We hereby certify the following Assay of 16 CORE samples submitted JAN-25-93 by D. JENKINS.

Sample Number	Cu %
18225	.429
18226	.220
18227	.233
18228	.202
18229	.530
18230	.335
18231	.380
18232	.322
18233	.263
18234	.329
18235	.330
18236	.199
18237	.301
18238	.242
18239	.207
18240	.237

Certified by _____

MIN-EN LABORATORIES

U - 95



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:
3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

3S-0010-RA1

Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attn: **B AINSWORTH/A SAVAGE/D JENKINS**

Date: **FEB-08-93**
Copy 1. **NEW CANAMIN RES. LTD., VANCOUVER, B.C.**
2. **DAVE JENKINS C/O MIN-EN SMITHERS, B.C.**

We hereby certify the following Assay of 23 CORE samples submitted FEB-03-93 by D. JENKINS.

Sample Number	Cu %
18251	.235
18252	.360
18253	.352
18254	.523
18255	.286
18256	.180
18257	.361
18258	.361
18259	.634
18260	.441
18261	.316
18262	.355
18263	.360
18264	.248
18265	.258
18266	.370
18267	.191
18268	.383
18269	.599
18270	.287
18271	.409
18272	.573
18273	.506

Certified by _____

MIN-EN LABORATORIES

II-96



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:
3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

3S-0006-RA1

Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attn: **B AINSWORTH/A SAVAGE/D JENKINS**

Date: **FEB-03-93**

Copy 1. **NEW CANAMIN RES. LTD., VANCOUVER, B.C.**
2. **DAVE JENKINS, C/O MIN-EN SMITHERS, B.C.**

We hereby certify the following Assay of 24 CORE samples submitted JAN-25-93 by D. JENKINS.

Sample Number	Cu %
18301	.661
18302	1.007
18303	.384
18304	.172
18305	.391
18306	.538
18307	.817
18308	.615
18309	.516
18310	.386
18311	.360
18312	.445
18313	.545
18314	.612
18351	.329
18352	.572
18353	.490
18354	.847
18355	.613
18356	.345
18357	.495
18358	.606
18359	.414
18360	.406

Certified by 

MIN-EN LABORATORIES

II-97



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:
3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

3S-0006-RA2

Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attn: **B AINSWORTH/A SAVAGE/D JENKINS**

Date: **FEB-03-93**
Copy 1. **NEW CANAMIN RES. LTD., VANCOUVER, B.C.**
2. **DAVE JENKINS, C/O MIN-EN SMITHERS, B.C.**

We hereby certify the following Assay of 24 CORE samples
submitted JAN-25-93 by D. JENKINS.

Sample Number	CU %
18361	.238
18362	.274
18363	.540
18364	.302
18365	.567
18366	.370
18367	.321
18368	.477
18369	.435
18370	.474
18371	.493
18372	.394
18373	.466
18374	.415
18375	.430
18376	.374
18377	.442
18378	.675
18379	.414
18380	.316
18381	.322
18382	.305
18383	.416
18384	.400

Certified by _____

MIN-EN LABORATORIES



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:
3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

3S-0006-RA3

Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attn: **B AINSWORTH/A SAVAGE/D JENKINS**

Date: **FEB-03-93**
Copy 1. **NEW CANAMIN RES. LTD., VANCOUVER, B.C.**
2. **DAVE JENKINS, C/O MIN-EN SMITHERS, B.C.**

We hereby certify the following Assay of 16 CORE samples submitted JAN-25-93 by D. JENKINS.

Sample Number	Cu %
18385	.227
18386	.341
18387	.166
18388	.238
18389	.199
18390	.462
18391	.533
18392	.424
18393	.574
18394	.285
18395	.305
18396	.194
18397	.387
18398	.350
18399	.395
18400	.891

Certified by _____

MIN-EN LABORATORIES



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:

705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:

3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

3S-0011-RA1

Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attn: **B AINSWORTH/A SAVAGE/D JENKINS**

Date: **FEB-08-93**

Copy 1. **NEW CANAMIN RES. LTD., VANCOUVER, B.C.**
2. **DAVE JENKINS C/O MIN-EN SMITHERS, B.C.**

We hereby certify the following Assay of 24 CORE samples submitted FEB-03-93 by D. JENKINS.

Sample Number	Cu %
18401	.328
18402	.300
18403	.398
18404	.261
18405	.211
18406	.319
18407	.266
18408	.242
18409	.210
18410	.183
18411	.469
18412	.340
18413	.577
18414	.615
18415	.172
18416	.132
18417	.116
18418	.224
18419	.235
18420	.181
18421	.502
18422	.548
18423	.435
18424	.458

Certified by _____

MIN-EN LABORATORIES



MIN-EN LABORATORIES
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:
3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

3S-0012-RA1

Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attn: **B AINSWORTH/A SAVAGE/D JENKINS**

Date: FEB-15-93
Copy 1. NEW CANAMIN RES. LTD., VANCOUVER, B.C.
2. DAVE JENKINS C/O MIN-EN SMITHERS, B.C.

We hereby certify the following Assay of 24 CORE samples submitted FEB-08-93 by D. JENKINS.

Sample Number	Cu %
18425	.712
18426	.656
18427	.597
18428	.437
18429	.291
18430	.413
18431	.632
18432	.318
18433	.267
18434	.260
18435	.099
18436	.116
18437	.187
18438	.269
18439	.201
18440	.249
18441	.237
18442	.648
18443	.890
18444	1.440
18445	.658
18446	.479
18447	1.305
18448	1.319

Certified by _____

MIN-EN LABORATORIES

II - 101



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:
3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

3S-0012-RA2

Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attn: **B AINSWORTH/A SAVAGE/D JENKINS**

Date: FEB-15-93
Copy 1. NEW CANAMIN RES. LTD., VANCOUVER, B.C.
2. DAVE JENKINS C/O MIN-EN SMITHERS, B.C.

We hereby certify the following Assay of 19 CORE samples submitted FEB-08-93 by D. JENKINS.

Sample Number	Cu %
18449	.659
18450	1.057
18451	.430
18452	.283
18453	.264
18454	.241
18455	.205
18456	.313
18457	.367
18458	.299
18459	.358
18460	.275
18461	.486
18462	.321
18463	.212
18464	.236
18465	.830
18466	.473
18467	.815

Certified by _____

MIN-EN LABORATORIES

II-102



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:
3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate


3S-0016-RA1

Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attn: **B AINSWORTH/A SAVAGE/D JENKINS**

Date: **FEB-23-93**
Copy 1. **NEW CANAMIN RES. LTD., VANCOUVER, B.C.**
2. **DAVE JENKINS, C/O MIN-EN SMITHERS, B.C.**

We hereby certify the following Assay of 24 CORE samples submitted FEB-16-93 by D. JENKINS.

Sample Number	Cu %
18468	.656
18469	.558
18470	.446
18471	.634
18472	.417
18473	.494
18474	.471
18475	.502
18476	.433
18477	.479
18478	.424
18479	.456
18480	.495
18481	.542
18482	.869
18483	1.487
18484	1.454
18485	.814
18486	1.075
18487	1.843
18488	.495
18489	.816
18490	.241
18491	.177

Certified by 

MIN-EN LABORATORIES

II-103



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:
3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

3S-0016-RA2

Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attn: **B AINSWORTH/A SAVAGE/D JENKINS**

Date: FEB-23-93

Copy 1. NEW CANAMIN RES. LTD., VANCOUVER, B.C.
2. DAVE JENKINS, C/O MIN-EN SMITHERS, B.C.

We hereby certify the following Assay of 7 CORE samples
submitted FEB-16-93 by D. JENKINS.

Sample Number	Cu %
18492	.202
18493	.458
18494	.341
18495	.286
18496	.373
18497	.404
18498	.468

Certified by _____

MIN-EN LABORATORIES

II-104



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:

705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:

3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

3S-0002-RA1


Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attn: **B.AINSWORTH/A.SAVAGE/D.JENKINS**

Date: **JAN-29-93**

Copy 1. **NEW CANAMIN RES. LTD., VANCOUVER, B.C.**
2. **DAVE JENKINS, C/O MIN-EN SMITHERS, B.C.**

We hereby certify the following Assay of 24 CORE samples submitted JAN-22-93 by DAVE JENKINS.

Sample Number	Cu %
18501	.486
18502	.320
18503	.611
18504	1.960
18505	.290
18506	.217
18507	.855
18508	.529
18509	.401
18510	.597
18511	1.235
18512	.176
18513	.095
18514	.119
18515	.396
18516	.134
18517	.111
18518	.083
18519	.046
18520	.143
18521	.214
18522	.176
18523	.453
18524	.165

Certified by 

MIN-EN LABORATORIES

II -105-



MIN-EN LABORATORIES
 (DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
 CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
 705 WEST 15TH STREET
 NORTH VANCOUVER, B.C. CANADA V7M 1T2
 TELEPHONE (604) 980-5814 OR (604) 988-4524
 FAX (604) 980-9621

SMITHERS LAB.:
 3176 TATLOW ROAD
 SMITHERS, B.C. CANADA V0J 2N0
 TELEPHONE (604) 847-3004
 FAX (604) 847-3005

Assay Certificate

3S-0002-RA2

Company: **NEW CANAMIN RESOURCES LTD.**
 Project: **HUCKLEBERRY**
 Attn: **B.AINSWORTH/A.SAVAGE/D.JENKINS**

Date: **JAN-29-93**

Copy 1. **NEW CANAMIN RES. LTD., VANCOUVER, B.C.**
 2. **DAVE JENKINS, C/O MIN-EN SMITHERS, B.C.**

We hereby certify the following Assay of 11 CORE samples submitted JAN-22-93 by DAVE JENKINS.

Sample Number	Cu %
18527	.478
18528	.310
18529	.841
18530	1.180
18531	.296
18532	.510
18533	.708
18534	.759
18535	.335
18536	.310
18537	.129

Certified by _____

MIN-EN LABORATORIES

II-106



MIN-EN LABORATORIES
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:
3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

3S-0017-RA1

Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attn: **B AINSWORTH/A SAVAGE/D JENKINS**

Date: FEB-25-93
Copy 1. **NEW CANAMIN RES. LTD., VANCOUVER, B.C.**
2. **DAVE JENKINS C/O MIN-EN SMITHERS, B.C.**

We hereby certify the following Assay of 23 CORE samples submitted FEB-16-93 by D. JENKINS.

Sample Number	Cu %
18551	.145
18552	.079
18553	.044
18554	.163
18555	.187
18556	.042
18557	.111
18558	.085
18559	.166
18560	.482
18561	.490
18562	.025
18563	.481
18564	.643
18565	.745
18566	.350
18567	.476
18568	.591
18569	.750
18570	.549
18571	.604
18572	.372
18573	.314

Certified by 

MIN-EN LABORATORIES

II -107



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:

705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:

3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

3S-0007-RA2

Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attn: **B AINSWORTH/A SAVAGE/D JENKINS**

Date: **FEB-02-93**
Copy 1. **NEW CANAMIN RES. LTD., VANCOUVER, B.C.**
2. **DAVE JENKINS C/O MIN-EN SMITHERS, B.C.**

We hereby certify the following Assay of 24 CORE samples submitted JAN-25-93 by D. JENKINS.

Sample Number	Cu %
18625	.128
18626	.112
18627	.111
18628	.078
18629	.171
18630	.400
18631	.398
18632	.303
18633	.304
18634	.193
18635	.384
18636	.460
18637	.382
18638	.291
18639	.326
18640	.440
18641	.304
18642	.340
18643	.538
18644	.652
18645	.201
18646	.277
18647	.523
18648	.460

Certified by 

MIN-EN LABORATORIES

II-109



MIN-EN LABORATORIES
 (DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
 CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
 705 WEST 15TH STREET
 NORTH VANCOUVER, B.C. CANADA V7M 1T2
 TELEPHONE (604) 980-5814 OR (604) 988-4524
 FAX (604) 980-9621

SMITHERS LAB.:
 3176 TATLOW ROAD
 SMITHERS, B.C. CANADA V0J 2N0
 TELEPHONE (604) 847-3004
 FAX (604) 847-3005

Assay Certificate

3S-0007-RA3

Company: **NEW CANAMIN RESOURCES LTD.**
 Project: **HUCKLEBERRY**
 Attn: **B AINSWORTH/A SAVAGE/D JENKINS**

Date: FEB-02-93

- Copy 1. NEW CANAMIN RES. LTD., VANCOUVER, B.C.
 2. DAVE JENKINS C/O MIN-EN SMITHERS, B.C.

We hereby certify the following Assay of 12 CORE samples submitted JAN-25-93 by D. JENKINS.

Sample Number	Cu %
18649	.815
18650	.402
18651	.465
18652	.520
18653	.462
18660	.571
18661	.338
18662	.473
18663	.410
18664	.399
18665	.314
18666	.260

Certified by _____

MIN-EN LABORATORIES



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:
3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

3S-0013-RA1


Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attn: **B AINSWORTH/A SAVAGE/D JENKINS**

Date: FEB-15-93

Copy 1. NEW CANAMIN RES. LTD., VANCOUVER, B.C.
2. DAVE JENKINS C/O MIN-EN SMITHERS, B.C.

We hereby certify the following Assay of 8 CORE samples submitted FEB-08-93 by D. JENKINS.

Sample Number	Cu %
18670	1.000
18671	.704
18672	.932
18673	.673
18674	.592
18675	.415
18676	.506
18677	.560

Certified by 
MIN-EN LABORATORIES

II -111



MIN-EN LABORATORIES
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:
3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

3S-0014-RA1

Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attn: **B AINSWORTH/A SAVAGE/D JENKINS**

Date: FEB-15-93

Copy 1. NEW CANAMIN RES. LTD., VANCOUVER, B.C.
2. DAVE JENKINS C/O MIN-EN SMITHERS, B.C.


We hereby certify the following Assay of 24 CORE samples submitted FEB-09-93 by D. JENKINS.

Sample Number	Cu %
18701	1.043
18702	.762
18703	.504
18704	.768
18705	.584
18706	.402
18707	.715
18708	.399
18709	.220
18710	.162
18711	.176
18712	.257
18713	.264
18714	.253
18715	.127
18716	.093
18717	.102
18718	.061
18719	.152
18720	.247
18721	.218
18722	.115
18723	.162
18724	.131

Certified by _____

MIN-EN LABORATORIES

II-112



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:
3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

3S-0014-RA2

Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Ass: **B AINSWORTH/A SAVAGE/D JENKINS**

Date: **FEB-15-93**
Copy 1. **NEW CANAMIN RES. LTD., VANCOUVER, B.C.**
2. **DAVE JENKINS C/O MIN-EN SMITHERS, B.C.**

We hereby certify the following Assay of 3 CORE samples submitted FEB-09-93 by D. JENKINS.

Sample Number	Cu %
18725	.132
18726	.155
18727	.200

Certified by 

MIN-EN LABORATORIES



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:
3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

3S-0018-RA1

Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attu: **B AINSWORTH/A SAVAGE/D JENKINS**

Date: **FEB-23-93**

Copy 1. **NEW CANAMIN RES. LTD., VANCOUVER, B.C.**
2. **DAVE JENKINS C/O MIN-EN SMITHERS, B.C.**

We hereby certify the following Assay of 24 CORE samples
submitted FEB-16-93 by D. JENKINS.

Sample Number	CU %
18751	.760
18752	.850
18753	.916
18754	.327
18755	.494
18756	.530
18757	.482
18758	.367
18759	.603
18760	.567
18761	.705
18762	.740
18763	.527
18764	.392
18765	.402
18766	.323
18767	.344
18768	.463
18769	.550
18770	.392
18771	.465
18772	.259
18773	.152
18774	.503

Certified by _____

[Signature]
MIN-EN LABORATORIES

II - 114



MIN-EN LABORATORIES
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:
3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

3S-0018-RA2

Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attn: **B AINSWORTH/A SAVAGE/D JENKINS**

Date: FEB-23-93

Copy 1. NEW CANAMIN RES. LTD., VANCOUVER, B.C.
2. DAVE JENKINS C/O MIN-EN SMITHERS, B.C.

We hereby certify the following Assay of 13 CORE samples submitted FEB-16-93 by D. JENKINS.

Sample Number	Cu %
18775	.390
18776	.195
18777	.373
18778	.258
18779	.178
18780	.135
18781	.151
18782	.196
18783	.176
18784	.338
18785	.192
18786	.182
18787	.188

Certified by 

MIN-EN LABORATORIES

II -115



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:

705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:

3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

3S-0024-RA1

Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attn: **B AINSWORTH/A SAVAGE/D JENKINS**

Date: **MAR-02-93**
Copy 1. NEW CANAMIN RES. LTD., VANCOUVER, B.C.

We hereby certify the following Assay of 24 CORE samples
submitted FEB-24-93 by DAVE JENKINS.

Sample Number	Cu %
18801	.638
18802	.786
18803	.588
18804	.649
18805	.542
18806	.603
18807	.419
18808	.522
18809	.570
18810	.722
18811	.617
18812	.641
18813	1.020
18814	.589
18815	.241
18816	.614
18817	.502
18818	.591
18819	.433
18820	.372
18821	.541
18822	.370
18823	.292
18824	.333

Certified by _____

MIN-EN LABORATORIES

II-116



MIN-EN LABORATORIES
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:

705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:

3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate


3S-0024-RA2

Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attn: **B AINSWORTH/A SAVAGE/D JENKINS**

Date: **MAR-02-93**
Copy 1. NEW CANAMIN RES. LTD., VANCOUVER, B.C.

We hereby certify the following Assay of 14 CORE samples submitted FEB-24-93 by DAVE JENKINS.

Sample Number	Cu %
18825	.268
18826	.199
18827	.347
18828	.389
18829	.250
18830	.184
18831	.163
18832	.331
18833	.221
18834	.653
18835	.550
18836	.358
18837	.301
18838	.101

Certified by 
MIN-EN LABORATORIES

II -117



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:
3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

3S-0019-RA1

Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attn: **B AINSWORTH/A SAVAGE/D JENKINS**

Date: FEB-23-93

We hereby certify the following Assay of 17 CORE samples submitted MMM-DD-YY by .

Sample Number	CU %
18851	.587
18852	.386
18853	.395
18854	.262
18855	.299
18856	.412
18857	.397
18858	.635
18859	.737
18860	.681
18861	.610
18862	.831
18863	.617
18864	.812
18865	.360
18866	.248
18867	.194

Certified by _____

MIN-EN LABORATORIES

II -118



MIN-EN LABORATORIES
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:
3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

3S-0020-RA1

Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attn: **B AINSWORTH/A SAVAGE/D JENKINS**

Date: **FEB-25-93**
Copy 1. **NEW CANAMIN RES. LTD., VANCOUVER, B.C.**
2. **DAVE JENKINS C/O MIN-EN SMITHERS, B.C.**

We hereby certify the following Assay of 24 CORE samples submitted FEB-16-93 by D. JENKINS.

Sample Number	Cu %
18901	.445
18902	.274
18903	1.060
18904	2.230
18905	.331
18906	.701
18907	.760
18908	.645
18909	.832
18910	.567
18911	.784
18912	1.025
18913	.986
18914	.586
18915	.425
18916	.422
18917	.419
18918	.553
18919	.842
18920	.415
18921	.416
18922	.280
18923	.383
18924	.447

Certified by 
MIN-EN LABORATORIES

II - 119



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:
3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

3S-0020-RA3

Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attn: **B AINSWORTH/A SAVAGE/D JENKINS**

Date: **FEB-25-93**
Copy 1. **NEW CANAMIN RES. LTD., VANCOUVER, B.C.**
2. **DAVE JENKINS C/O MIN-EN SMITHERS, B.C.**


We hereby certify the following Assay of 24 CORE samples submitted FEB-16-93 by D. JENKINS.

Sample Number	Cu %
18962	.458
18963	.525
18964	.776
18965	.572
18966	.301
18967	.244
18968	.220
18969	.335
18970	.169
18971	.128
18972	.394
18973	.511
18974	.206
18975	.187
18976	.214
18977	.347
18978	.698
18979	.504
18980	.315
18981	.378
18982	.237
18983	.194
18984	.236
18985	.226

Certified by 

MIN-EN LABORATORIES

121-11



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:
3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

3S-0020-RA4

Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attn: **B AINSWORTH/A SAVAGE/D JENKINS**

Date: **FEB-25-93**
Copy 1. **NEW CANAMIN RES. LTD., VANCOUVER, B.C.**
2. **DAVE JENKINS C/O MIN-EN SMITHERS, B.C.**

We hereby certify the following Assay of 3 CORE samples submitted FEB-16-93 by D. JENKINS.

Sample Number	Cu %
18986	.418
18987	.310
18988	.584

Certified by _____

MIN-EN LABORATORIES

II - 122



**MIN
• EN
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
705 WEST 15TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4524
FAX (604) 980-9621

SMITHERS LAB.:
3176 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

3S-0029-RA1

Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attn: **B AINSWORTH/A SAVAGE/D JENKINS**

Date: **MAR-10-93**
Copy 1. **NEW CANAMIN RES. LTD., VANCOUVER, B.C.**

We hereby certify the following Assay of 7 CORE samples
submitted MAR-08-93 by K. ILLERBRUN.

Sample Number	Cu %
923401	.028
923402	.017
923403	.019
923404	.026
923405	.054
923406	.035
923407	.028

Certified by 

MIN-EN LABORATORIES

II - 123



**MINERAL
ENVIRONMENTS
LABORATORIES**
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:

705 WEST 18TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-1824
FAX (604) 980-9621

SMITHERS LAB.:

3178 TITLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3005

Assay Certificate

35-0030-RA1

Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attr: **B AINSWORTH/A SAVAGE/D JENKINS**

Date: **MAR-10-93**

Copy 1. NEW CANAMIN RES. LTD., VANCOUVER, B.C.


We hereby certify the following Assay of 9 CORE samples
submitted MAR-08-93 by K. ILLERBRUN.

Sample Number		CU %	DRILL HOLE NO.
932301	45-50	.054	93-23
932302		.112	
932303	@ 5 ft int	.062	
932304		.042	
932305		.068	
932306	70-80	.091	
932307	@ 10 ft int	.091	
932308		.053	
932309	100-110 (bottom)	.083	

Certified by 

MIN-EN LABORATORIES

II -124



MIN-EN LABORATORIES
(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSTS • GEOCHEMISTS

VANCOUVER OFFICE:
105 WEST 18TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-9614 OR (604) 989-4624
FAX (604) 980-9621

SMITHERS LAB.:
3178 TATLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3008

Assay Certificate

35-0029-RA1

Company: **NEW CANAMEN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attn: **B AINSWORTH/A SAVAGE/D JENKINS**

Date: **MAR-10-93**
Copy 1. **NEW CANAMEN RES. LTD., VANCOUVER, B.C.**

We hereby certify the following Assay of 7 CORE samples submitted MAR-08-93 by K. ILLERBRUN.

Sample Number	CU %	DRILL HOLE NO.
932401		93-24
923401	0-55 .028	
923402	.017	
923403	@ 5 ft int .019	
923404	.026	
923405	.054	
923406	80-90 .035	
923407	932407.90-98 .028 (bottom)	

Certified by _____

MIN-EN LABORATORIES

II-125



MINERAL ENVIRONMENTS LABORATORIES

(DIVISION OF ASSAYERS CORP.)

SPECIALISTS IN MINERAL ENVIRONMENTS
CHEMISTS • ASSAYERS • ANALYSIS • GEOCHEMISTS

VANCOUVER OFFICE:
706 WEST 16TH STREET
NORTH VANCOUVER, B.C. CANADA V7M 1T2
TELEPHONE (604) 980-5814 OR (604) 988-4824
FAX (604) 980-9821

SMITHERS LAB:
3176 KILLOW ROAD
SMITHERS, B.C. CANADA V0J 2N0
TELEPHONE (604) 847-3004
FAX (604) 847-3006

Assay Certificate

3S-0031-RA1

Company: **NEW CANAMIN RESOURCES LTD.**
Project: **HUCKLEBERRY**
Attn: **B AINSWORTH/A SAVAGE/D JENKINS**

Date: **MAR-10-93**
Copy 1. NEW CANAMIN RES. LTD., VANCOUVER, B.C.

We hereby certify the following Assay of 1 CORE samples submitted MAR-08-93 by K. ILLERBRUN,

Sample Number	Cu %	DRILL HOLE NO.
932801 75-85 (bottom)	.021	93-28

Certified by _____

MIN-EN LABORATORIES

II-127

New Canamin Resources

Huckleberry

HOLE#	INTERVAL(feet)		SAMPLE	AG	AS	CD	CU	K	MO	NI	PB	TI	ZN	W	AU	CU-ASSAY
HOLE#	START	END	SAMPLE	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPB	%
92-1	35	60	40551	0.1	1	0.1	1464	0.54	8	1	5	1756	60	7	15	0.151
92-1	60	70	40552	0.1	1	0.1	3761	0.93	117	1	7	1935	48	6	54	0.404
92-1	70	80	40553	0.8	1	0.1	3441	0.30	99	1	11	1251	39	5	153	0.345
92-1	80	90	40554	0.7	1	0.1	3766	0.29	101	1	12	656	36	4	184	0.399
92-1	90	100	40555	0.6	1	0.1	3707	0.20	56	1	7	2846	42	5	132	0.377
92-1	100	110	40556	0.9	1	0.1	2737	0.34	74	1	9	2468	45	6	72	0.281
92-1	110	120	40557	0.8	1	0.1	3019	0.45	433	1	8	2343	46	5	156	0.292
92-1	120	130	40558	0.8	1	0.1	3235	0.36	180	1	10	1750	44	5	190	0.320
92-1	130	140	40559	1.0	1	0.1	6077	0.47	39	1	11	933	50	4	205	0.647
92-1	140	150	40560	1.2	1	0.1	3050	0.46	193	1	17	1031	46	5	54	0.323
92-1	150	160	40561	0.6	1	0.1	2908	0.33	149	1	10	985	47	4	32	0.276
92-1	160	170	40562	0.7	1	0.1	2791	0.26	17	1	7	1229	42	4	49	0.294
92-1	170	180	40563	1.0	1	0.1	4436	0.88	62	1	10	2294	50	5	75	0.477
92-1	180	190	40564	0.1	1	0.1	2462	1.14	45	1	48	3194	134	6	42	0.273
92-1	190	200	40565	0.1	1	0.1	3345	0.78	46	1	6	2987	53	7	61	0.369
92-1	200	210	40566	0.1	1	0.1	3677	1.49	12	1	1	3835	54	7	59	0.402
92-1	210	220	40567	0.1	1	0.1	2590	0.85	63	1	5	2827	47	6	49	0.277
92-1	220	230	40568	0.7	1	0.1	1502	0.26	84	1	9	1014	33	5	11	0.158
92-1	230	240	40569	0.5	1	0.1	843	0.23	35	1	9	959	35	4	10	0.089
92-1	240	250	40570	0.4	3	0.1	542	0.22	178	1	11	647	35	5	2	0.056
92-1	250	260	40571	0.4	1	0.1	986	0.20	48	1	8	1208	38	5	8	0.103
92-1	260	270	40572	0.8	1	0.1	1338	0.39	94	2	12	468	33	7	40	0.140
92-1	270	280	40573	0.7	2	0.1	1284	0.35	56	1	13	409	36	5	42	0.141
92-1	280	290	40574	1.4	14	2.1	1260	0.36	97	3	232	136	388	5	252	0.135
92-1	290	300	40575	0.5	11	0.1	1342	0.26	85	3	18	100	28	6	27	0.147
92-1	300	310	40576	0.9	3	0.1	2639	0.25	70	4	10	64	33	6	46	0.270
92-1	310	320	40577	0.3	8	0.1	1241	0.28	56	3	10	164	38	9	25	0.120
92-1	320	330	40578	0.7	5	0.1	1391	0.34	226	4	10	104	29	7	29	0.151
92-1	330	340	40579	0.7	5	0.1	1503	0.38	99	4	13	189	35	9	28	0.153
92-1	340	350	40580	0.9	1	0.1	3208	0.38	174	3	15	332	34	7	72	0.325
92-1	350	360	40581	0.9	8	0.1	1946	0.33	75	2	12	327	33	9	34	0.198
92-1	360	370	40582	1.2	4	0.1	3523	0.24	102	5	12	227	35	9	67	0.353
92-1	370	380	40583	0.1	1	0.1	5843	0.79	34	2	12	2029	48	11	118	0.609
92-1	380	390	40584	0.1	1	0.1	6615	1.19	396	1	10	2692	59	9	83	0.678
92-1	390	400	40585	0.1	1	0.1	6187	1.18	38	1	6	3011	57	11	125	0.688

New Canamin Resources

Huckleberry

Min-En Laboratories
 705 West 15th St.
 North Vancouver, B.C.
 Tel. (604) 980-5814

HOLE#	INTERVAL(feet)		SAMPLE	AG	AS	CD	CU	K	MO	NI	PB	TI	ZN	W	AU	CU-ASSAY
HOLE#	START	END	SAMPLE	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPB	%
92-1	400	410	40586	0.1	1	0.1	2776	0.43	102	1	6	976	54	6	88	0.315
92-1	410	420	40587	0.1	1	0.1	5009	0.46	7	1	3	2874	64	9	70	0.546
92-1	420	430	40588	0.1	1	0.1	5752	0.63	86	1	7	2950	66	8	87	0.640
92-1	430	440	40589	0.1	1	0.1	1973	0.93	4	1	1	3361	54	9	41	0.218
92-1	440	450	40590	0.1	1	0.1	3492	0.54	6	1	5	2991	56	9	61	0.347
92-1	450	460	40591	0.1	1	0.1	8434	1.13	81	1	8	3261	72	11	161	0.860
92-1	460	470	40592	0.1	1	0.1	4092	0.53	10	1	1	3035	57	8	56	0.441
92-1	470	480	40593	0.1	1	0.1	3317	0.56	23	1	4	2943	54	9	59	0.368
92-1	480	490	40594	0.1	1	0.1	3048	0.98	42	1	1	3573	56	9	63	0.339
92-1	490	500	40595	1.3	1	0.1	2010	1.16	28	1	5	2887	43	5	33	0.227
92-1	500	510	40596	0.4	1	0.1	3157	0.93	29	7	7	2183	40	8	50	0.342

621-II

New Canamin Resources

Huckleberry

HOLE#	INTERVAL(feet)		SAMPLE	AG	AS	CD	CU	K	MO	NI	PB	TI	ZN	W	AU	CU-ASSAY
HOLE#	START	END	SAMPLE	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPB	%
92-2	60	70	40601	0.1	1	0.1	4819	0.79	34	1	9	1603	59	5	88	0.522
92-2	70	80	40602	0.5	1	0.1	3504	0.45	273	2	6	521	34	5	46	0.382
92-2	80	90	40603	0.6	1	0.1	1774	0.26	113	3	8	296	34	8	18	0.198
92-2	90	100	40604	0.9	1	0.1	1569	0.40	149	4	5	408	32	8	23	0.171
92-2	100	110	40605	1.0	3	0.1	2601	0.48	263	2	51	351	64	5	68	0.275
92-2	110	120	40606	0.3	1	0.1	1036	0.22	91	3	4	914	36	7	11	0.120
92-2	120	130	40607	0.5	1	0.1	2271	0.18	63	2	4	625	37	6	31	0.254
92-2	130	140	40608	0.6	1	0.1	2681	0.17	128	2	8	437	35	5	34	0.300
92-2	140	150	40609	0.7	1	0.1	2290	0.16	138	3	4	316	32	5	42	0.259
92-2	150	160	40610	0.6	1	0.1	1586	0.16	68	1	3	467	34	5	20	0.176
92-2	160	170	40611	0.8	2	0.1	2556	0.25	100	3	8	87	34	4	21	0.282
92-2	170	180	40612	0.8	1	0.1	2469	0.23	109	3	5	397	30	7	16	0.256
92-2	180	190	40613	0.9	1	0.1	3143	0.12	125	4	5	777	38	5	54	0.325
92-2	190	200	40614	1.1	1	0.1	3868	0.17	163	2	7	298	33	5	78	0.431
92-2	200	210	40615	0.9	1	0.1	4540	0.24	70	11	8	689	39	8	95	0.490
92-2	210	220	40616	0.1	1	0.1	6115	0.89	306	18	1	1698	41	10	87	0.700
92-2	220	230	40617	1.4	6	0.1	3560	0.32	132	5	6	102	27	5	61	0.389
92-2	230	240	40618	0.7	1	0.1	4143	0.48	200	4	8	1132	31	6	75	0.404
92-2	240	250	40619	0.1	1	0.1	6324	0.57	216	1	1	2871	41	10	208	0.657
92-2	250	260	40620	0.1	1	0.1	8311	1.39	152	1	1	4247	46	10	290	0.830
92-2	260	270	40621	0.1	1	0.1	10000	0.91	63	4	3	3435	42	9	369	1.160
92-2	270	280	40622	0.1	1	0.1	9209	1.00	137	1	1	3530	49	8	196	0.890
92-2	280	290	40623	0.1	1	0.1	9061	1.01	115	1	1	3722	45	9	147	0.880
92-2	290	300	40624	0.1	1	0.1	8686	1.21	191	4	1	3195	44	8	305	0.840
92-2	300	310	40625	0.1	1	0.1	4638	1.01	102	19	1	2153	52	7	108	0.538
92-2	310	320	40626	3.1	1	0.1	10000	1.00	476	6	1	2186	41	8	313	1.270
92-2	320	330	40627	1.8	1	0.1	10000	0.32	158	10	3	551	39	8	320	1.070
92-2	330	340	40628	0.6	1	0.1	8556	0.70	262	6	1	1546	55	7	196	0.840
92-2	340	350	40629	0.1	1	0.1	5091	1.01	180	2	1	2274	55	7	88	0.584
92-2	350	360	40630	1.5	1	0.1	4983	0.54	171	3	4	975	48	5	108	0.557
92-2	360	370	40631	0.3	1	0.1	4255	0.67	141	1	1	1323	48	5	61	0.481
92-2	370	380	40632	0.4	1	0.1	4093	0.72	90	3	1	1870	46	6	38	0.416
92-2	380	390	40633	0.8	1	0.1	2611	0.29	128	8	1	514	35	5	28	0.283
92-2	390	400	40634	0.7	1	0.1	1708	0.36	403	7	4	322	31	6	20	0.184
92-2	400	410	40635	0.4	1	0.1	1156	0.28	108	7	6	130	24	6	11	0.123

II-13C

New Canamin Resources

Huckleberry

Min-En Laboratories
 705 West 15th St.
 North Vancouver, B.C.
 Tel. (604) 980-5814

HOLE#	INTERVAL(feet)		SAMPLE	AG	AS	CD	CU	K	MO	NI	PB	TI	ZN	W	AU	CU-ASSAY
HOLE#	START	END	SAMPLE	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPB	%
92-2	410	420	40636	0.1	1	0.1	1617	0.35	116	4	3	840	34	5	20	0.174
92-2	420	430	40637	0.7	1	0.1	3174	0.26	204	5	5	970	41	5	42	0.338
92-2	430	440	40638	1.0	1	0.1	2968	0.32	164	8	1	1635	40	8	30	0.319
92-2	440	450	40639	1.9	1	0.1	2851	0.36	131	9	1	1378	39	6	42	0.309
92-2	450	460	40640	1.1	1	0.1	2627	0.28	103	7	1	1626	39	6	35	0.286
92-2	460	470	40641	0.6	1	0.1	2077	0.19	121	8	1	1940	42	7	16	0.216
92-2	470	480	40642	0.5	1	0.1	2316	0.17	369	6	3	871	42	7	27	0.259
92-2	480	490	40643	0.4	1	0.1	1991	0.16	147	7	2	1533	46	6	39	0.213
92-2	490	500	40644	0.7	1	0.1	3049	0.21	184	6	13	1815	70	7	42	0.326
92-2	500	510	40645	1.1	1	0.1	2856	0.45	94	7	2	2052	40	7	26	0.314
92-2	510	520	40646	0.6	1	0.1	2558	0.48	101	5	1	2053	41	6	44	0.272
92-2	520	530	40647	0.6	1	0.1	1925	0.35	36	7	1	1759	27	7	28	0.214
92-2	530	540	40648	0.9	1	0.1	1920	0.39	113	7	4	1799	26	8	17	0.204
92-2	540	550	40649	1.3	1	0.1	3005	0.43	575	8	1	1680	37	6	45	0.308

II - 131

New Canamin Resources

Huckleberry

HOLE#	INTERVAL(feet)		SAMPLE	AG	AS	CD	CU	K	MO	NI	PB	TI	ZN	W	AU	CU-ASSAY
HOLE#	START	END	SAMPLE	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPB	%
92-3	50	60	40651	1.4	1	0.1	5808	0.37	208	1	18	1271	51	14	37	0.546
92-3	60	70	40652	1.4	1	0.1	5655	0.38	39	1	4	1283	52	9	69	0.570
92-3	70	80	40653	1.6	1	0.1	4315	0.47	40	1	2	2165	54	11	82	0.463
92-3	80	90	40654	2.0	1	0.1	6048	0.19	154	1	7	1434	50	8	85	0.642
92-3	90	100	40655	2.1	1	0.1	4832	0.68	146	1	1	2411	42	8	94	0.517
92-3	100	110	40656	1.0	1	0.1	4532	0.85	106	1	1	2826	44	7	73	0.486
92-3	110	120	40657	0.1	1	0.1	5445	0.92	212	1	1	2351	49	7	133	0.631
92-3	120	130	40658	0.1	1	0.1	6780	0.91	186	1	1	2677	47	8	119	0.801
92-3	130	140	40659	0.1	1	0.1	4791	0.69	98	1	1	2062	46	9	89	0.550
92-3	140	150	40660	0.1	1	0.1	3697	0.60	76	1	1	2381	41	8	74	0.433
92-3	150	160	40661	1.3	1	0.1	6584	0.68	168	3	35	1977	245	9	119	0.834
92-3	160	170	40662	0.9	1	0.1	4102	0.59	98	1	52	1490	52	8	72	0.493
92-3	170	180	40663	1.8	5	0.1	5210	0.12	112	3	7	81	30	7	95	0.641
92-3	180	190	40664	1.7	6	0.1	4245	0.11	312	5	5	69	29	5	69	0.538
92-3	190	200	40665	2.0	4	0.1	4390	0.10	81	5	4	66	28	5	83	0.567
92-3	200	210	40666	1.0	19	0.1	3167	0.30	301	5	44	656	533	5	62	0.408
92-3	210	220	40667	0.9	1	0.1	2847	0.26	103	8	1	1595	46	10	63	0.305
92-3	220	230	40668	0.5	1	0.1	2170	0.22	115	6	1	1630	45	7	57	0.235
92-3	230	240	40669	0.2	1	0.1	2078	0.19	67	8	1	1460	45	11	34	0.224
92-3	240	250	40670	0.4	1	0.1	2179	0.14	102	7	1	859	41	6	28	0.239
92-3	250	260	40671	0.8	1	0.1	3671	0.23	203	9	1	679	37	8	52	0.414
92-3	260	270	40672	0.6	1	0.1	2711	0.19	233	4	1	1836	41	7	55	0.303
92-3	270	280	40673	0.3	1	0.1	2622	0.21	69	7	1	1374	45	8	34	0.278
92-3	280	290	40674	0.8	1	0.1	3661	0.17	196	6	3	1341	39	6	38	0.404
92-3	290	300	40675	0.2	1	0.1	2041	0.26	472	6	1	1568	45	9	23	0.206
92-3	300	310	40676	0.4	1	0.1	2557	0.26	331	7	18	1197	55	7	55	0.265
92-3	310	320	40677	0.4	1	0.1	2733	0.28	252	9	1	1674	39	9	37	0.281
92-3	320	330	40678	0.8	1	0.1	2725	0.44	137	8	1	1573	39	8	28	0.273
92-3	330	340	40679	0.1	1	0.1	1922	0.48	259	9	2	1201	43	10	26	0.179
92-3	340	350	40680	0.1	1	0.1	1662	0.59	125	8	1	979	42	7	25	0.158

II-132

New Canamin Resources

Huckleberry

 Min-En Laboratories
 705 West 15th St.
 North Vancouver, B.C.
 Tel. (604) 980-5814

HOLE#	INTERVAL(feet)		SAMPLE	AG	AS	CD	CU	K	MO	NI	PB	TI	ZN	W	AU	CU-ASSAY
HOLE#	START	END	SAMPLE	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPB	%
92-4	40	50	40701	0.4	1	0.1	2664	0.66	21	1	1	2647	51	7	41	0.249
92-4	50	60	40702	1.3	1	0.1	6421	0.67	73	1	1	1433	45	6	85	0.603
92-4	60	70	40703	0.6	1	0.1	3959	0.43	66	1	2	1117	41	8	63	0.381
92-4	70	80	40704	1.8	1	0.1	8710	1.36	167	1	1	2120	45	6	89	0.828
92-4	80	90	40705	0.1	10	0.1	4788	1.49	108	1	1	2033	67	6	76	0.475
92-4	90	100	40706	0.1	517	0.1	7112	0.80	170	4	162	729	496	5	98	0.690
92-4	100	110	40707	3.1	735	0.1	5139	0.53	1288	8	312	89	745	8	94	0.474
92-4	110	120	40708	2.7	502	3.4	2421	0.38	1282	22	246	20	681	7	273	0.232
92-4	120	130	40709	0.8	140	0.1	3039	0.61	1298	7	29	266	131	8	86	0.294
92-4	130	140	40710	0.1	1	0.1	2787	1.21	274	15	1	1159	66	8	50	0.286
92-4	140	150	40711	0.3	1	0.1	4017	0.77	144	7	7	895	88	9	45	0.388
92-4	150	160	40712	0.2	1	0.1	1429	0.45	30	2	1	570	35	7	24	0.142
92-4	160	170	40713	0.4	1	0.1	1298	0.43	99	3	1	454	34	10	18	0.137
92-4	170	180	40714	0.5	1	0.1	1892	0.33	182	1	1	260	29	6	37	0.201
92-4	180	190	40715	0.8	1	0.1	2825	0.34	252	1	1	146	35	6	31	0.308
92-4	190	200	40716	0.1	1	0.1	1087	0.23	50	1	1	405	35	4	18	0.121
92-4	200	210	40717	0.9	1	0.1	2300	0.21	85	4	1	372	30	10	38	0.261
92-4	210	220	40718	0.8	1	0.1	3160	0.38	76	8	1	919	32	7	50	0.365
92-4	220	230	40719	1.1	1	0.1	3794	0.60	187	6	1	1160	38	7	45	0.403
92-4	230	240	40720	0.7	1	0.1	2092	0.35	291	5	4	201	50	6	30	0.230
92-4	240	250	40721	1.0	3	0.1	1489	0.24	71	3	6	13	44	4	22	0.168
92-4	250	260	40722	0.9	2	0.1	1992	0.30	155	5	22	11	65	6	28	0.218
92-4	260	270	40723	1.3	3	0.1	2867	0.34	208	4	8	25	22	4	36	0.311
92-4	270	280	40724	0.7	1	0.1	2039	0.45	98	3	1	390	38	8	30	0.202
92-4	280	290	40725	1.6	2	0.1	2651	0.22	216	7	4	160	28	5	39	0.298
92-4	290	300	40726	0.1	1	0.1	4525	1.77	86	1	1	3199	53	9	44	0.490
92-4	300	310	40727	0.1	1	0.1	3845	0.83	11	1	1	1690	53	9	45	0.397
92-4	310	320	40728	0.1	1	0.1	5292	1.14	54	1	1	1674	50	7	70	0.603
92-4	320	330	40729	0.1	1	0.1	3505	0.64	20	1	1	952	86	7	89	0.373
92-4	330	340	40730	0.1	1	0.1	4717	0.71	102	1	1	1392	86	11	101	0.494
92-4	340	350	40731	0.1	1	0.1	7329	1.18	9	1	1	2696	74	12	78	0.799
92-4	350	360	40732	0.1	1	0.1	8076	0.84	26	1	1	2065	58	9	87	0.800
92-4	360	370	40733	0.1	1	0.1	7877	0.75	442	3	1	1424	61	8	88	0.833
92-4	370	380	40734	0.2	1	0.1	10000	0.95	258	8	1	2074	84	11	195	0.980
92-4	380	390	40735	2.7	1	0.1	10000	0.83	124	9	1	1583	70	13	146	1.170

New Canamin Resources

Huckleberry

Min-En Laboratories
 705 West 15th St.
 North Vancouver, B.C.
 Tel. (604) 980-5814

HOLE#	INTERVAL(feet)		SAMPLE	AG	AS	CD	CU	K	MO	NI	PB	TI	ZN	W	AU	CU-ASSAY
HOLE#	START	END	SAMPLE	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPB	%
92-4	390	400	40736	1.3	1	0.1	4472	0.34	151	1	39	510	42	7	57	0.459
92-4	400	410	40737	0.5	1	0.1	4590	0.82	212	1	113	1225	380	9	77	0.483
92-4	410	420	40738	1.2	1	0.1	5166	0.74	204	3	1	1543	61	9	61	0.555
92-4	420	430	40739	1.4	1	0.1	5206	0.66	128	1	8	1420	68	9	88	0.562
92-4	430	440	40740	0.3	1	0.1	4039	0.59	47	4	5	1202	45	7	63	0.434
92-4	440	450	40741	0.5	1	0.1	3360	0.68	76	5	1	1757	44	10	48	0.355
92-4	450	460	40742	1.1	1	0.1	3977	0.30	217	8	5	617	42	10	59	0.409
92-4	460	470	40743	1.3	1	0.1	4683	0.16	211	6	6	410	33	9	66	0.514
92-4	470	480	40744	1.0	1	0.1	7774	0.50	287	7	7	857	49	5	108	0.802
92-4	480	490	40745	1.0	1	0.1	10000	0.75	187	14	1	2391	87	7	221	1.660
92-4	490	500	40746	0.1	1	0.1	9975	1.06	72	1	1	3708	66	7	146	0.980

II-134

New Canamin Resources

Huckleberry

HOLE#	INTERVAL(feet)		SAMPLE	AG	AS	CD	CU	K	MO	NI	PB	TI	ZN	W	AU	CU-ASSAY
HOLE#	START	END	SAMPLE	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPB	%
92-5	32	40	40751	0.1	1	0.1	2334	0.30	21	1	1	3478	45	9	36	0.243
92-5	40	50	40752	0.1	1	0.1	8296	0.31	41	1	1	3060	60	7	100	0.800
92-5	50	60	40753	0.1	1	0.1	6402	0.27	25	1	1	3518	52	9	143	0.698
92-5	60	70	40754	0.1	1	0.1	5475	0.33	42	1	1	3060	51	6	125	0.598
92-5	70	80	40755	3.3	1	0.1	7768	0.57	54	1	3	2849	58	7	104	0.840
92-5	80	90	40756	0.1	1	0.1	4534	0.45	118	1	1	2823	44	5	83	0.518
92-5	90	100	40757	0.1	1	0.1	4202	0.50	12	1	1	3031	32	5	50	0.397
92-5	100	110	40758	0.1	1	0.1	5831	0.86	69	1	1	2825	36	3	123	0.550
92-5	110	120	40759	0.1	1	0.1	4373	0.88	73	1	1	1627	27	4	67	0.432
92-5	120	130	40760	0.1	1	0.1	9185	0.99	45	1	1	1920	68	4	110	0.847
92-5	130	140	40761	0.3	1	0.1	9481	0.92	43	10	1	2368	33	5	122	0.860
92-5	140	150	40762	0.1	1	0.1	4822	0.52	68	1	1	2474	26	3	60	0.461
92-5	150	160	40763	0.1	1	0.1	6825	0.33	28	1	1	860	28	3	109	0.683
92-5	160	170	40764	0.5	1	0.1	8094	0.35	51	1	1	489	34	5	108	0.777
92-5	170	180	40765	0.1	1	0.1	4548	0.25	27	1	1	1283	28	4	51	0.458
92-5	180	190	40766	0.1	1	0.1	3841	0.34	39	1	1	1100	23	3	60	0.368
92-5	190	200	40767	0.9	1	0.1	7220	0.20	59	1	1	2498	33	4	124	0.656
92-5	200	210	40768	1.8	1	0.1	3145	0.32	21	1	16	2628	75	3	36	0.290
92-5	210	220	40769	0.1	1	0.1	3179	0.26	26	1	1	2896	29	4	62	0.319
92-5	220	230	40770	1.3	1	0.1	4490	0.29	23	1	1	3243	30	4	59	0.437
92-5	230	240	40771	2.0	1	0.1	5907	0.28	90	1	1	907	53	3	107	0.661
92-5	240	250	40772	1.3	1	0.1	4512	0.40	194	1	6	1073	48	4	82	0.500
92-5	250	260	40773	1.0	1	0.1	5994	1.31	77	1	1	2909	58	5	126	0.637
92-5	260	270	40774	0.5	1	0.1	8650	1.00	33	1	1	3116	66	7	197	0.880
92-5	270	280	40775	0.9	1	0.1	8879	0.91	106	1	1	3205	55	6	135	0.940
92-5	280	290	40776	1.1	1	0.1	5980	0.57	52	2	1	2149	44	6	103	0.644
92-5	290	300	40777	0.7	1	0.1	6513	0.82	65	1	1	2557	49	6	94	0.764
92-5	300	310	40778	0.3	1	0.1	3605	0.60	64	1	1	2183	42	5	68	0.436
92-5	310	320	40779	0.1	1	0.1	5565	1.06	147	1	1	3064	50	7	94	0.635
92-5	320	330	40780	0.1	1	0.1	5392	0.93	67	1	1	2757	57	7	125	0.596
92-5	330	340	40781	0.4	1	0.1	6913	0.83	27	1	1	2840	56	7	140	0.815
92-5	340	350	40782	0.1	1	0.1	3212	0.78	52	1	1	2460	49	6	50	0.365
92-5	350	360	40783	0.1	1	0.1	3889	0.88	52	1	1	2903	51	7	87	0.460
92-5	360	370	40784	0.1	1	0.1	3516	0.61	23	1	1	2391	52	5	71	0.457
92-5	370	380	40785	0.2	1	0.1	5590	0.35	22	1	1	1855	51	7	111	0.709

New Canamin Resources

Huckleberry

Min-En Laboratories
 705 West 15th St.
 North Vancouver, B.C.
 Tel. (604) 980-5814

HOLE#	INTERVAL(feet)		SAMPLE	AG	AS	CD	CU	K	MO	NI	PB	TI	ZN	W	AU	CU-ASSAY
HOLE#	START	END	SAMPLE	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPB	%
92-5	380	390	40786	0.1	1	0.1	3666	0.36	121	1	1	1714	52	6	68	0.466
92-5	390	400	40787	0.1	1	0.1	4265	0.53	65	1	1	1882	51	5	97	0.554
92-5	400	410	40788	0.4	1	0.1	5375	0.87	248	1	1	3081	63	6	104	0.670
92-5	410	420	40789	0.3	1	0.1	4358	0.83	67	1	1	2444	59	7	75	0.502
92-5	420	430	40790	0.1	1	0.1	4148	0.54	53	1	1	1967	60	7	52	0.488
92-5	430	440	40791	0.1	1	0.1	2212	0.56	70	1	1	1518	56	6	38	0.262
92-5	440	450	40792	0.1	1	0.1	3768	0.63	35	1	1	1650	55	7	56	0.483
92-5	450	460	40793	0.1	1	0.1	2768	0.72	43	1	1	1814	48	6	50	0.381
92-5	460	470	40794	0.1	1	0.1	4248	0.80	77	1	1	1602	55	5	134	0.455
92-5	470	480	40795	0.1	1	0.1	1870	0.59	26	1	1	1806	38	2	28	0.203
92-5	480	490	40796	0.1	1	0.1	3104	0.61	33	1	1	2523	41	3	42	0.294
92-5	490	500	40797	0.1	1	0.1	2470	0.83	43	1	1	2664	45	4	46	0.252

H-136

New Canamin Resources

Huckleberry

Min-En Laboratories
 705 West 15th St.
 North Vancouver, B.C.
 Tel. (604) 980-5814

HOLE#	INTERVAL(feet)		SAMPLE	AG	AS	CD	CU	K	MO	NI	PB	TI	ZN	W	AU	CU-ASSAY
HOLE#	START	END	SAMPLE	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPB	%
92-6	50	60	40801	0.1	1	0.1	4643	0.50	65	1	1	3374	50	3	90	0.505
92-6	60	70	40802	0.3	1	0.1	8857	0.67	93	1	1	3746	59	4	136	0.850
92-6	70	80	40803	0.8	1	0.1	10000	0.77	58	1	1	3832	63	4	183	1.020
92-6	80	90	40804	0.1	1	0.1	8739	0.67	35	1	1	3935	56	5	154	0.860
92-6	90	100	40805	0.1	1	0.1	4504	0.63	72	1	1	2985	40	5	104	0.502
92-6	100	110	40806	0.7	1	0.1	5940	0.45	68	1	1	2528	42	8	108	0.597
92-6	110	120	40807	1.4	1	0.1	10000	0.75	5	2	1	2207	54	7	231	1.210
92-6	120	130	40808	0.2	1	0.1	7208	0.63	26	1	3	2184	42	4	153	0.847
92-6	130	140	40809	2.5	4	0.1	7756	0.47	739	6	20	1007	86	5	89	0.850
92-6	140	150	40810	1.8	1	0.1	7022	0.54	75	1	1	1495	31	2	127	0.816
92-6	150	160	40811	0.1	1	0.1	4214	0.58	50	1	1	1924	49	2	94	0.476
92-6	160	170	40812	0.1	1	0.1	2856	0.74	20	1	1	2143	44	2	41	0.356
92-6	170	180	40813	0.1	1	0.1	3209	0.80	73	1	1	2646	42	3	42	0.406
92-6	180	190	40814	0.1	1	0.1	4923	0.77	8	1	1	2782	51	3	98	0.586
92-6	190	200	40815	0.8	1	0.1	4017	0.38	12	1	1	2163	43	2	94	0.490
92-6	200	210	40816	0.9	1	0.1	3671	0.23	30	1	4	1808	41	4	86	0.447
92-6	210	220	40817	0.8	1	0.1	2259	0.24	16	1	46	983	202	1	53	0.285
92-6	220	230	40818	5.2	88	4.4	2310	0.29	13	4	1463	274	658	1	90	0.302
92-6	230	240	40820	37.3	503	31.8	7184	0.32	46	6	633	368	1796	2	210	0.870
92-6	240	250	40821	0.8	1	0.1	2667	0.24	39	5	20	549	58	2	50	0.357
92-6	250	260	40822	0.3	1	0.1	2014	0.26	7	4	5	589	43	2	37	0.257
92-6	260	270	40823	4.1	28	93.9	2468	0.33	674	8	63	533	7458	8	51	0.269
92-6	270	280	40824	0.1	1	0.1	1655	0.20	7	7	1	1051	82	5	24	0.177
92-6	280	290	40825	0.1	1	0.1	1398	0.17	24	7	1	716	71	4	20	0.155

451-137

New Canamin Resources

Huckleberry

HOLE#	INTERVAL(feet)		SAMPLE	AG	AS	CD	CU	K	MO	NI	PB	TI	ZN	W	AU	CU-ASSAY
HOLE#	START	END	SAMPLE	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPB	%
92-7	30	40	40851	0.1	1	0.1	7325	0.60	56	1	1	2040	49	5	126	0.836
92-7	40	50	40852	0.1	1	0.1	4497	0.59	44	1	1	2655	52	6	80	0.491
92-7	50	60	40853	0.1	1	0.1	5649	0.64	26	1	1	2971	52	6	76	0.647
92-7	60	70	40854	0.6	1	0.1	8911	1.01	41	1	1	3556	60	8	124	0.880
92-7	70	80	40855	0.3	1	0.1	7731	1.27	40	22	1	2919	64	12	143	0.770
92-7	80	90	40856	1.0	1	0.1	4001	0.75	30	1	2	2002	39	5	76	0.396
92-7	90	100	40857	2.0	1	0.1	7024	0.64	83	6	9	1344	44	5	86	0.674
92-7	100	110	40858	2.4	1	0.1	8582	0.75	291	10	5	2532	51	7	147	0.850
92-7	110	120	40859	1.8	1	0.1	8307	0.82	99	20	10	2218	60	11	159	0.830
92-7	120	130	40860	1.5	1	0.1	5052	0.34	376	8	9	1261	42	7	76	0.552
92-7	130	140	40861	2.3	1	0.1	5825	0.22	130	5	8	462	38	6	92	0.597
92-7	140	150	40862	1.9	4	0.1	3661	0.24	327	4	10	58	23	6	73	0.384
92-7	150	160	40863	2.0	1	0.1	4156	0.22	117	6	9	133	24	6	64	0.440
92-7	160	170	40864	1.5	11	0.1	3134	0.16	131	6	8	420	29	6	47	0.355
92-7	170	180	40865	1.6	1	0.1	8277	0.95	50	31	1	2189	59	10	124	0.840
92-7	180	190	40866	1.3	1	0.1	6272	1.10	119	21	1	2416	47	11	90	0.661
92-7	190	200	40867	1.5	1	0.1	3687	0.45	224	1	4	2156	35	6	65	0.423
92-7	200	210	40868	1.6	1	0.1	6347	0.65	208	3	6	1874	38	6	96	0.678
92-7	210	220	40869	0.4	1	0.1	5453	1.19	203	1	1	3090	45	7	90	0.592
92-7	220	230	40870	0.5	1	0.1	4751	1.05	23	1	5	3074	50	7	65	0.500
92-7	230	240	40871	1.9	1	0.1	4842	0.54	30	1	3	2376	45	6	89	0.555
92-7	240	250	40872	1.7	1	0.1	7521	0.98	78	15	5	2375	54	8	168	0.828
92-7	250	260	40873	1.8	1	0.1	5396	0.56	57	6	6	1973	40	6	91	0.623
92-7	260	270	40874	0.1	1	0.1	3378	1.03	10	1	1	3186	46	7	60	0.377
92-7	270	280	40875	0.1	1	0.1	3443	1.14	98	1	1	2451	42	6	69	0.410
92-7	280	290	40876	0.1	1	0.1	4266	1.07	20	1	5	2739	43	6	58	0.457
92-7	290	300	40877	0.5	1	0.1	4731	1.07	121	1	2	2428	38	6	58	0.525
92-7	300	310	40878	0.2	1	0.1	3616	0.80	61	1	5	2330	43	6	47	0.387
92-7	310	320	40879	0.1	1	0.1	6342	1.26	18	1	1	3041	56	7	144	0.692
92-7	320	330	40880	0.1	1	0.1	4993	1.03	55	1	1	2868	52	7	69	0.542
92-7	330	340	40881	0.1	1	0.1	3474	1.31	49	1	1	3335	47	7	71	0.376
92-7	340	350	40882	0.1	1	0.1	3665	0.95	38	1	1	3199	46	6	51	0.387
92-7	350	360	40883	0.1	1	0.1	2991	0.72	12	1	1	2649	45	6	46	0.319
92-7	360	370	40884	0.1	1	0.1	3829	1.15	96	1	1	2633	44	6	48	0.419
92-7	370	380	40885	0.6	1	0.1	3157	1.18	75	1	2	2289	40	6	50	0.317

II-138

New Canamin Resources

Huckleberry

Min-En Laboratories
 705 West 15th St.
 North Vancouver, B.C.
 Tel. (604) 980-5814

HOLE#	INTERVAL(feet)		SAMPLE	AG	AS	CD	CU	K	MO	NI	PB	TI	ZN	W	AU	CU-ASSAY
HOLE#	START	END	SAMPLE	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPB	%
92-7	380	390	40886	0.6	1	0.1	4746	0.73	58	4	1	2063	46	6	112	0.523
92-7	390	400	40887	0.1	1	0.1	3907	1.12	14	4	1	2621	48	6	63	0.404

681-11

New Canamin Resources

Huckleberry

Min-En Laboratories
705 West 15th St.
North Vancouver, B.C.
Tel. (604) 980-5814

HOLE#	INTERVAL(feet)		SAMPLE	AG	AS	CD	CU	K	MO	NI	PB	TI	ZN	W	AU	CU-ASSAY
HOLE#	START	END	SAMPLE	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPB	%
92-8	60	70	40901	2.1	81	0.1	3400	0.47	388	3	80	315	99	5	65	0.357
92-8	70	80	40902	0.3	1	0.1	2864	0.69	84	1	15	1033	49	5	67	0.358
92-8	80	90	40903	1.0	4	0.1	1536	0.39	105	2	12	201	26	3	34	0.162
92-8	90	100	40904	2.3	314	0.1	3433	0.28	101	3	48	71	162	3	93	0.378
92-8	100	110	40905	0.9	74	0.1	1688	0.58	58	1	21	884	66	7	36	0.181
92-8	110	120	40906	0.3	1	0.1	2322	1.49	614	1	1	3153	39	6	38	0.240
92-8	120	130	40907	1.8	1	0.1	6198	1.00	41	1	12	1888	45	6	104	0.680
92-8	130	140	40908	1.2	1	0.1	3683	1.01	58	1	8	1971	60	5	64	0.395
92-8	140	150	40909	1.5	1	0.1	5022	0.65	19	1	35	1128	100	5	78	0.537
92-8	150	160	40910	1.2	1	0.1	2947	0.38	36	3	14	262	34	5	24	0.320
92-8	160	170	40911	1.9	34	0.1	3863	0.33	228	3	57	54	203	3	91	0.427
92-8	170	180	40912	1.3	44	1.2	3645	0.47	223	2	101	403	469	4	81	0.386
92-8	180	190	40913	1.4	1	0.1	3915	0.33	55	3	14	277	32	5	90	0.408
92-8	190	200	40914	1.4	1	0.1	4047	0.27	265	4	13	314	36	5	109	0.413
92-8	200	210	40915	1.3	1	0.1	3185	0.36	187	4	17	321	39	7	73	0.339
92-8	210	220	40916	1.1	1	0.1	4172	0.37	87	4	7	638	39	5	118	0.437
92-8	220	230	40917	1.4	1	0.1	5931	0.54	91	6	17	1054	43	6	138	0.616
92-8	230	240	40918	0.3	1	0.1	4046	0.60	79	3	19	1261	41	9	72	0.402
92-8	240	250	40919	0.7	1	0.1	4085	0.84	85	1	33	1761	58	7	93	0.417
92-8	250	260	40920	1.6	1	0.1	4181	0.28	111	4	22	105	65	3	91	0.455
92-8	260	270	40921	2.0	56	0.1	1870	0.13	83	3	33	411	213	4	30	0.207
92-8	270	280	40922	0.7	1	0.1	1556	0.08	36	3	12	641	37	5	26	0.168
92-8	280	290	40923	0.7	1	0.1	1326	0.06	23	1	4	1182	30	7	19	0.137
92-8	290	300	40924	1.0	1	0.1	1605	0.09	69	3	9	1470	35	8	18	0.172
92-8	300	310	40925	0.5	1	0.1	1117	0.09	15	5	10	857	31	7	13	0.115

241 - II

New Canamin Resources

Huckleberry

Min-En Laboratories
 705 West 15th St.
 North Vancouver, B.C.
 Tel. (604) 980-5814

HOLE#	INTERVAL(feet)		SAMPLE	AG	AS	CD	CU	K	MO	NI	PB	TI	ZN	W	AU	CU-ASSAY
HOLE#	START	END	SAMPLE	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPB	%
92-8A	60	70	40951	0.1	1	0.1	1415	0.30	201	1	13	272	36	5	16	0.149
92-8A	70	80	40952	0.7	1	0.1	2835	0.52	80	1	9	964	36	5	54	0.304
92-8A	80	90	40953	0.8	1	0.1	3841	0.39	112	1	4	710	42	6	77	0.408
92-8A	90	100	40954	1.3	72	9.3	2709	0.24	71	1	30	224	800	4	51	0.288
92-8A	100	110	40955	1.1	1	0.1	3138	0.27	201	4	9	161	54	7	42	0.340
92-8A	110	115	40956	0.1	1	0.1	2545	0.35	63	5	5	481	41	5	32	0.275

141-II

New Canamin Resources

Huckleberry

Min-En Laboratories
705 West 15th St.
North Vancouver, B.C.
Tel. (604) 980-5814

HOLE#	INTERVAL(feet)		SAMPLE	AG	AS	CD	CU	K	MO	NI	PB	TI	ZN	W	AU	CU-ASSAY
HOLE#	START	END	SAMPLE	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPB	%
92-8E	70	80	40957	0.8	1	0.1	2801	0.48	140	2	48	706	64	6	66	0.321
92-8E	80	90	40958	0.4	1	0.1	3244	0.64	35	1	6	1913	46	8	79	0.348
92-8E	90	100	40959	0.1	1	0.1	3989	0.62	212	2	6	1688	47	8	68	0.417
92-8E	100	110	40960	0.1	1	0.1	4782	0.71	54	6	5	1830	52	6	89	0.521
92-8E	110	120	40961	0.1	1	0.1	4315	1.04	101	6	1	2238	51	7	76	0.449
92-8E	120	130	40962	0.1	1	0.1	3672	1.47	81	8	1	2783	45	9	55	0.403
92-8E	130	140	40963	1.1	1	0.1	4306	1.28	119	1	1	3165	46	7	47	0.475
92-8E	140	150	40964	0.1	1	0.1	3578	1.08	35	1	1	2543	49	8	52	0.402
92-8E	150	160	40965	0.1	1	0.1	4870	1.10	109	2	1	2356	54	8	76	0.544
92-8E	160	170	40966	0.1	1	0.1	4052	0.55	21	1	1	2023	49	9	59	0.439
92-8E	170	180	40967	0.1	1	0.1	5720	0.84	233	1	4	1607	47	9	33	0.612
92-8E	180	190	40968	0.1	1	0.1	6357	0.93	140	1	6	1944	48	7	112	0.761
92-8E	190	200	40969	0.1	1	0.1	7007	1.34	97	1	1	2859	55	11	91	0.815

241-II

New Canamin Resources

Huckleberry

 Min-En Laboratories
 705 West 15th St.
 North Vancouver, B.C.
 Tel. (604) 980-5814

HOLE#	INTERVAL(feet)		SAMPLE	AG	AS	CD	CU	K	MO	NI	PB	TI	ZN	W	AU	CU-ASSAY
HOLE#	START	END	SAMPLE	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPB	%
92-9	60	70	15001	1.3	1	0.1	4347	0.84	454	7	6	1777	40	6	72	0.500
92-9	70	80	15002	0.1	1	0.1	2838	2.09	16	19	1	3095	53	11	32	0.318
92-9	80	90	15003	0.1	1	0.1	3374	1.33	39	14	1	2837	45	9	44	0.347
92-9	90	100	15004	0.8	1	0.1	3333	1.11	74	6	1	2384	45	8	53	0.339
92-9	100	110	15005	2.1	1	0.1	8550	0.32	117	7	4	2108	50	8	112	0.844
92-9	110	120	15006	2.5	1	0.1	10000	0.38	258	7	10	1608	54	10	138	1.090
92-9	120	130	15007	1.4	1	0.1	7518	0.68	186	1	1	1906	51	7	99	0.754
92-9	130	140	15008	0.6	1	0.1	4096	0.58	170	1	16	1446	78	7	69	0.428
92-9	140	150	15009	0.2	1	0.1	3242	0.74	211	1	1	2179	43	7	42	0.334
92-9	150	160	15010	0.3	1	0.1	3539	0.70	184	1	1	1958	45	8	136	0.354
92-9	160	170	15011	0.1	1	0.1	1710	0.43	167	1	3	1112	39	7	20	0.168
92-9	170	180	15012	0.3	1	0.1	3967	0.58	107	1	4	1565	41	7	55	0.408
92-9	180	190	15013	1.0	1	0.1	3784	0.38	511	2	10	516	37	6	59	0.389
92-9	190	200	15014	0.8	1	0.1	6038	0.35	289	1	6	634	43	6	79	0.611
92-9	200	210	15015	0.8	1	0.1	4335	0.34	358	1	9	651	39	5	53	0.425
92-9	210	220	15016	0.6	1	0.1	3645	0.54	233	1	2	1206	42	6	50	0.370
92-9	220	230	15017	0.5	1	0.1	4227	0.92	92	1	1	2591	47	7	49	0.430
92-9	230	240	15018	0.1	1	0.1	3773	0.66	183	1	1	1381	43	6	51	0.398
92-9	240	250	15019	0.1	1	0.1	6465	1.20	102	1	1	2450	60	8	83	0.677
92-9	250	260	15020	0.1	1	0.1	5494	0.80	133	3	1	1579	48	7	73	0.588
92-9	260	270	15021	0.1	1	0.1	2076	0.58	46	55	1	1830	68	7	29	0.217
92-9	270	280	15022	0.1	1	0.1	2768	0.29	94	67	1	1722	75	8	33	0.294
92-9	280	290	15023	1.5	1	0.1	6111	0.49	270	5	12	1166	53	6	58	0.656
92-9	290	300	15024	1.3	1	0.1	4422	0.59	100	1	7	1220	47	7	40	0.459
92-9	300	310	15025	1.1	1	0.1	7694	0.78	184	1	7	1705	62	8	76	0.800
92-9	310	320	15026	1.8	1	0.1	9221	0.44	420	1	17	1177	66	7	128	1.040
92-9	320	330	15027	0.7	1	0.1	9118	0.64	109	1	7	1674	71	7	112	0.960
92-9	330	340	15028	1.2	1	0.1	8789	0.55	72	1	5	1610	77	8	108	0.856
92-9	340	350	15029	0.1	1	0.1	7280	0.97	33	1	1	2701	67	7	85	0.747
92-9	350	360	15030	0.1	1	0.1	7494	0.80	221	1	3	3008	70	9	150	0.782
92-9	360	370	15031	0.5	1	0.1	6821	0.55	49	1	4	2618	62	7	144	0.724
92-9	370	380	15032	1.5	1	0.1	9453	0.20	74	1	17	1450	85	9	197	1.050
92-9	380	390	15033	0.7	1	0.1	4959	0.15	53	3	10	821	51	6	121	0.511
92-9	390	400	15034	1.3	1	0.1	6025	0.15	85	6	9	636	43	7	101	0.602
92-9	400	410	15035	3.1	1	0.1	9994	0.12	43	17	27	1607	60	7	249	1.060

New Canamin Resources

Huckleberry

Min-En Laboratories
 705 West 15th St.
 North Vancouver, B.C.
 Tel. (604) 980-5814

HOLE#	INTERVAL(feet)		SAMPLE	AG	AS	CD	CU	K	MO	NI	PB	TI	ZN	W	AU	CU-ASSAY
HOLE#	START	END	SAMPLE	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPB	%
92-9	410	420	15036	1.6	1	0.1	6520	0.34	50	16	11	1224	50	9	198	0.695
92-9	420	430	15037	0.1	1	0.1	3203	0.21	63	6	5	956	41	7	73	0.342
92-9	430	440	15038	0.3	1	0.1	2110	0.16	351	8	10	701	36	8	33	0.229

661-11

New Canamin Resources

Huckleberry

Min-En Laboratories
705 West 15th St.
North Vancouver, B.C.
Tel. (604) 980-5814

HOLE#	INTERVAL(feet)		SAMPLE	AG	AS	CD	CU	K	MO	NI	PB	TI	ZN	W	AU	CU-ASSAY
HOLE#	START	END	SAMPLE	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPB	%
92-10	70	80	15051	0.1	1	0.1	4968	0.72	33	1	3	2116	61	8	58	0.545
92-10	80	90	15052	0.1	1	0.1	4037	1.17	27	1	1	2501	64	20	34	0.402
92-10	90	100	15053	0.1	1	0.1	4888	0.88	1088	1	1	2039	42	9	90	0.525
92-10	100	110	15054	0.1	1	0.1	9719	1.12	74	1	1	2837	54	9	117	1.090
92-10	110	120	15055	0.1	1	0.1	3259	0.84	163	1	1	2650	53	9	66	0.351
92-10	120	130	15056	1.0	1	0.1	5617	0.51	200	1	6	1306	47	7	82	0.602
92-10	130	140	15057	0.2	1	0.1	4020	0.58	176	5	1	1596	40	7	80	0.440
92-10	140	150	15058	1.6	1	0.1	4891	0.34	148	2	3	791	48	8	76	0.551
92-10	150	160	15059	0.1	1	0.1	5566	0.91	27	1	1	1991	50	6	98	0.582
92-10	160	170	15060	0.1	1	0.1	4220	1.02	156	1	1	2464	48	6	58	0.457
92-10	170	180	15061	0.1	1	0.1	4802	0.90	38	1	1	3142	60	8	88	0.521
92-10	180	190	15062	0.1	1	0.1	7701	0.80	167	1	4	3022	66	8	90	0.880
92-10	190	200	15063	0.9	1	0.1	10000	0.82	24	5	8	2954	65	10	214	1.050
92-10	200	210	15064	0.1	1	0.1	10000	0.62	369	8	6	2212	63	9	198	1.120
92-10	210	220	15065	0.7	1	0.1	6878	0.51	213	11	8	1067	49	9	148	0.759
92-10	220	230	15066	0.5	1	0.1	3272	0.19	175	12	10	810	42	8	82	0.341
92-10	230	240	15067	0.5	1	0.1	3760	0.14	361	16	7	798	40	8	101	0.406
92-10	240	250	15068	0.8	1	0.1	3340	0.14	96	12	10	782	45	7	102	0.353
92-10	250	260	15069	1.3	1	0.1	4822	0.19	327	17	8	1421	41	10	129	0.500
92-10	260	270	15070	0.6	1	0.1	1549	0.09	213	4	7	1094	35	7	18	0.166
92-10	270	280	15071	0.6	1	0.1	1202	0.11	191	9	6	1032	37	8	29	0.130
92-10	280	290	15072	0.1	1	0.1	965	0.10	90	7	5	463	40	8	23	0.110

-SK- II

New Canamin Resources

Huckleberry

Min-En Laboratories
 705 West 15th St.
 North Vancouver, B.C.
 Tel. (604) 980-5814

HOLE#	INTERVAL(feet)		SAMPLE	AG	AS	CD	CU	K	MO	NI	PB	TI	ZN	W	AU	CU-ASSAY
HOLE#	START	END	SAMPLE	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPB	%
92-11	75	80	15101	0.1	1	0.1	5630	0.63	1	1	1	3103	52	10	110	0.668
92-11	80	90	15102	0.1	1	0.1	3877	0.39	7	1	2	3121	41	9	77	0.453
92-11	90	100	15103	0.1	1	0.1	6640	0.67	71	1	1	2726	47	11	111	0.702
92-11	100	110	15104	0.1	1	0.1	8307	1.17	43	7	1	2777	50	7	95	0.990
92-11	110	120	15105	0.7	1	0.1	9738	1.08	101	17	2	2341	56	9	84	1.030
92-11	120	130	15106	4.6	1	0.1	10000	0.44	57	7	13	1690	48	13	161	1.740
92-11	130	140	15107	1.3	1	0.1	6111	0.69	126	10	3	1768	44	9	81	0.658
92-11	140	150	15108	0.1	1	0.1	4805	0.89	54	1	1	2979	47	9	70	0.548
92-11	150	160	15109	0.1	1	0.1	5599	1.42	94	8	1	3335	48	8	87	0.655
92-11	160	170	15110	0.1	1	0.1	5295	0.48	47	1	1	2723	50	9	104	0.636
92-11	170	180	15111	0.1	1	0.1	7939	0.55	71	1	3	2866	57	10	135	0.930
92-11	180	190	15112	2.5	1	0.1	10000	0.63	100	7	16	2889	42	10	236	1.540
92-11	190	200	15113	1.7	1	0.1	10000	0.77	102	7	6	2952	43	10	218	1.560
92-11	200	210	15114	1.9	1	0.1	10000	0.53	111	6	9	2373	48	10	179	1.280
92-11	210	220	15115	1.7	1	0.1	10000	0.82	664	5	10	2872	63	11	224	1.800
92-11	220	230	15116	1.5	1	0.1	10000	0.67	238	2	9	2793	64	13	221	1.690
92-11	230	240	15117	3.9	1	0.1	10000	0.63	296	1	4	2643	57	8	143	1.060
92-11	240	250	15118	0.1	1	0.1	6377	0.74	280	1	1	2545	60	10	122	0.667
92-11	250	260	15119	0.6	1	0.1	3552	0.16	749	12	5	741	45	10	50	0.372
92-11	260	270	15120	0.8	1	0.1	4854	0.21	142	8	4	771	56	8	85	0.490
92-11	270	280	15121	1.1	1	0.1	4122	0.10	50	9	6	640	52	7	40	0.418
92-11	280	290	15122	0.3	1	0.1	2639	0.08	38	5	1	1297	48	9	37	0.275
92-11	290	300	15123	0.4	1	0.1	2646	0.16	102	9	2	1311	41	8	39	0.272
92-11	300	310	15124	0.5	1	0.1	2631	0.24	317	5	1	1658	41	9	41	0.273
92-11	310	320	15125	0.9	1	0.1	3692	0.26	310	7	1	1526	44	6	61	0.388
92-11	320	330	15126	1.5	1	0.1	4609	0.37	221	6	3	1212	45	10	68	0.479
92-11	330	340	15127	1.1	1	0.1	3535	0.14	136	8	1	221	30	5	58	0.388
92-11	340	350	15128	0.2	1	0.1	3757	0.54	112	20	1	1462	42	7	62	0.421
92-11	350	360	15129	0.1	1	0.1	3386	1.49	76	22	1	3404	50	10	53	0.396
92-11	360	370	15130	0.4	1	0.1	3536	0.81	112	11	1	2555	44	9	48	0.375

92-11-II

New Canamin Resources

Huckleberry

Min-En Laboratories
705 West 15th St.
North Vancouver, B.C.
Tel. (604) 980-5814

HOLE#	INTERVAL(feet)		SAMPLE	AG	AS	CD	CU	K	MO	NI	PB	TI	ZN	W	AU	CU-ASSAY
HOLE#	START	END	SAMPLE	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPB	%
92-12	20	30	15151	0.8	1	0.1	7816	1.13	74	1	1	3137	54	8	89	0.801
92-12	30	40	15152	1.6	1	0.1	6493	0.37	186	1	6	1820	50	9	141	0.665
92-12	40	50	15153	0.5	1	0.1	6735	0.49	15	1	2	2770	47	7	96	0.716
92-12	50	60	15154	3.3	1	0.1	10000	0.51	28	1	5	3012	64	9	243	1.330
92-12	60	70	15155	0.1	1	0.1	4802	0.82	33	13	1	2211	56	11	81	0.469
92-12	70	80	15156	0.6	1	0.1	8012	0.95	12	23	1	2268	62	11	147	0.794
92-12	80	90	15157	0.1	1	0.1	4415	0.67	43	7	1	1781	42	9	62	0.478
92-12	90	100	15158	0.1	1	0.1	2481	0.57	47	9	1	1536	36	9	22	0.248
92-12	100	110	15159	0.1	1	0.1	4048	0.76	19	1	1	2438	42	7	54	0.414
92-12	110	120	15160	0.2	1	0.1	8209	1.09	39	1	1	2472	63	10	139	0.870
92-12	120	130	15161	0.1	1	0.1	6626	0.67	50	2	1	1952	48	8	130	0.718
92-12	130	140	15162	0.2	1	0.1	6068	0.63	5	1	1	2905	46	8	72	0.646
92-12	140	150	15163	0.5	1	0.1	7484	0.44	433	1	1	2767	52	7	139	0.789
92-12	150	160	15164	0.1	1	0.1	5337	0.53	18	1	6	2087	67	6	117	0.619
92-12	160	170	15165	0.1	1	0.1	3969	0.64	90	1	1	2919	63	7	84	0.420
92-12	170	180	15166	0.1	1	0.1	5609	0.43	31	1	2	3014	65	8	146	0.601
92-12	180	190	15167	0.1	1	0.1	2186	0.85	24	1	1	3057	57	7	46	0.220
92-12	190	200	15168	0.3	1	0.1	3930	0.85	101	1	1	2919	62	7	49	0.388
92-12	200	220	15169	0.1	1	0.1	2571	0.65	15	1	1	2935	58	8	34	0.253
92-12	220	230	15170	0.1	1	0.1	6302	0.69	14	1	1	2137	62	8	120	0.632
92-12	230	240	15171	0.1	1	0.1	2462	0.59	29	1	1	1036	57	4	88	0.267
92-12	240	250	15172	0.7	1	0.1	1739	0.18	39	1	1	310	44	3	26	0.182
92-12	250	260	15173	1.4	1	0.1	3530	0.28	54	1	1	593	45	3	72	0.411
92-12	260	270	15174	0.7	1	0.1	2124	0.26	43	1	1	588	52	3	51	0.218
92-12	270	280	15175	1.4	1	0.1	3018	0.27	18	1	4	600	42	5	75	0.309
92-12	280	290	15176	1.8	1	0.1	3016	0.25	45	1	3	531	41	5	64	0.321
92-12	290	300	15177	0.8	1	0.1	2880	0.79	70	11	1	1501	50	9	63	0.305
92-12	300	310	15178	1.4	1	0.1	3092	0.29	58	1	7	657	50	5	75	0.326

11-147

New Canamin Resources

Huckleberry

HOLE#	INTERVAL(feet)		SAMPLE	AG	AS	CD	CU	K	MO	NI	PB	TI	ZN	W	AU	CU-ASSAY
HOLE#	START	END	SAMPLE	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPB	%
92-13	20	30	15201	0.1	1	0.1	1241	0.33	1	1	3	2456	69	7	30	0.132
92-13	30	40	15202	1.7	1	0.1	5101	0.57	104	1	5	2198	69	6	116	0.576
92-13	40	50	15203	0.8	1	0.1	4826	0.75	31	1	1	2918	66	8	110	0.505
92-13	50	60	15204	0.4	1	0.1	2085	0.59	31	1	7	3246	66	8	45	0.225
92-13	60	70	15205	0.1	1	0.1	2665	0.97	61	2	1	2519	53	7	46	0.281
92-13	70	80	15206	0.9	1	0.1	5898	0.92	39	1	11	2211	89	7	151	0.666
92-13	80	90	15207	1.1	1	0.1	5326	0.91	124	1	6	2110	62	6	70	0.585
92-13	90	100	15208	2.1	1	0.1	5552	0.85	90	1	25	1789	147	7	120	0.602
92-13	100	110	15209	1.7	1	0.1	6174	0.49	79	1	13	990	59	6	122	0.684
92-13	110	120	15210	0.6	1	0.1	5893	0.20	184	1	9	821	61	6	152	0.653
92-13	120	130	15211	0.3	1	0.1	4209	0.29	87	1	3	1867	59	7	89	0.480
92-13	130	140	15212	3.0	1	0.1	10000	0.29	143	1	5	3225	83	10	147	1.170
92-13	140	150	15213	1.4	1	0.1	6483	0.34	24	1	5	2837	65	7	120	0.727
92-13	150	160	15214	2.9	1	0.1	10000	0.60	65	1	7	3096	80	8	150	1.190
92-13	160	170	15215	0.2	1	0.1	2100	0.54	51	1	11	2815	91	8	95	0.233
92-13	170	180	15216	0.6	1	0.1	5093	0.46	54	1	1	2702	65	7	93	0.613
92-13	180	190	15217	1.3	1	0.1	6255	1.15	55	1	1	3568	78	8	122	0.708
92-13	190	200	15218	0.1	1	0.1	4155	0.60	45	1	1	3305	62	9	80	0.454
92-13	200	210	15219	0.1	1	0.1	3854	0.40	38	1	30	2068	113	9	183	0.474
92-13	210	220	15220	1.3	1	0.1	7641	0.29	23	1	9	2370	73	9	107	0.980
92-13	220	230	15221	0.2	1	0.1	4576	0.37	22	1	2	2924	60	10	152	0.576
92-13	230	240	15222	1.1	1	0.1	7348	0.51	60	1	8	2779	75	8	195	0.960
92-13	240	250	15223	0.1	1	0.1	3870	0.49	265	1	4	2503	66	9	115	0.479
92-13	250	260	15224	0.8	1	0.1	3248	0.83	61	1	1	2309	55	7	110	0.771
92-13	260	270	15225	0.8	1	0.1	3132	0.78	63	1	1	2192	52	7	79	0.421
92-13	270	280	15226	0.6	1	0.1	2672	0.50	59	1	1	1888	53	7	67	0.363
92-13	280	290	15227	0.6	1	0.1	3093	0.84	21	1	1	2323	53	9	90	0.404
92-13	290	300	15228	2.0	1	0.1	5314	0.77	15	1	3	2666	60	8	114	0.760
92-13	300	310	15229	1.3	1	0.1	6509	0.83	39	1	1	3748	66	10	103	0.668
92-13	310	320	15230	1.8	1	0.1	8321	0.67	62	1	1	3558	72	8	154	0.890
92-13	320	330	15231	2.7	1	0.1	9448	0.40	49	1	1	2757	65	10	422	1.020
92-13	330	340	15232	1.5	1	0.1	5777	0.61	82	7	1	2395	51	8	113	0.626
92-13	340	350	15233	2.1	1	0.1	8800	0.75	160	30	1	2232	60	13	184	0.940
92-13	350	360	15234	0.1	1	0.1	4957	0.90	76	4	1	2746	56	9	74	0.548
92-13	360	370	15235	0.1	1	0.1	4103	1.00	83	1	1	3385	54	7	61	0.431

New Canamin Resources

Huckleberry

 Min-En Laboratories
 705 West 15th St.
 North Vancouver, B.C.
 Tel. (604) 980-5814

HOLE#	INTERVAL(feet)		SAMPLE	AG	AS	CD	CU	K	MO	NI	PB	TI	ZN	W	AU	CU-ASSAY
HOLE#	START	END	SAMPLE	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPB	%
92-13	370	380	15236	0.1	1	0.1	4663	1.06	55	1	1	3337	54	7	79	0.516
92-13	380	390	15237	0.1	1	0.1	6493	0.69	74	1	1	3231	63	8	84	0.669
92-13	390	400	15238	0.1	1	0.1	4964	0.98	211	1	1	3592	60	10	85	0.535
92-13	400	410	15239	0.1	1	0.1	5044	1.18	9	1	1	3285	62	9	73	0.524
92-13	410	420	15240	0.6	1	0.1	6508	1.06	90	1	1	3589	58	8	116	0.715
92-13	420	430	15241	0.1	1	0.1	9561	0.99	326	3	1	2138	64	8	137	1.080
92-13	430	440	15242	1.5	1	0.1	7499	0.66	128	3	1	1255	52	5	141	0.910
92-13	440	450	15243	0.1	1	0.1	6474	1.32	17	1	1	2627	58	7	105	0.691
92-13	450	460	15244	0.1	1	0.1	3635	0.91	23	1	1	1998	53	8	35	0.412
92-13	460	470	15245	0.1	1	0.1	4697	1.08	7	1	1	2217	56	7	77	0.520
92-13	470	480	15246	0.1	1	0.1	4004	1.31	49	1	1	2573	53	6	70	0.440
92-13	480	490	15247	0.1	1	0.1	4369	1.47	35	1	1	3033	51	8	100	0.473
92-13	490	500	15248	0.1	1	0.1	2236	1.17	66	1	1	2389	52	8	28	0.235

641-11

New Canamin Resources

Huckleberry

Min-En Laboratories
705 West 15th St.
North Vancouver, B.C.
Tel. (604) 980-5814

HOLE#	INTERVAL(feet)		SAMPLE	AG	AS	CD	CU	K	MO	NI	PB	TI	ZN	W	AU	CU-ASSAY
HOLE#	START	END	SAMPLE	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPB	%
92-14	30	40	15251	0.8	1	0.1	5991	0.42	63	10	3	2513	44	9	130	0.652
92-14	40	50	15252	0.1	1	0.1	5756	0.86	69	2	1	3410	49	11	94	0.576
92-14	50	60	15253	1.1	1	0.1	6526	1.06	94	13	1	2837	52	11	117	0.730
92-14	60	70	15254	0.4	1	0.1	5574	1.00	49	22	1	2498	50	13	109	0.622
92-14	70	80	15255	0.1	1	0.1	2804	0.87	16	1	1	2806	48	11	82	0.311
92-14	80	90	15256	0.1	1	0.1	2559	0.88	123	1	1	2338	47	8	89	0.285
92-14	90	100	15257	0.8	1	0.1	3791	0.56	112	1	1	1894	43	7	86	0.424
92-14	100	110	15258	1.1	1	0.1	2314	0.55	120	5	1	967	31	8	46	0.236
92-14	110	130	15259	1.1	1	0.1	2592	0.42	56	3	3	865	32	7	52	0.282
92-14	130	140	15261	1.2	1	0.1	3619	0.30	52	3	6	608	35	6	114	0.405
92-14	140	150	15262	1.1	1	0.1	4486	0.63	63	2	3	1470	48	8	95	0.489
92-14	150	160	15263	0.5	1	0.1	4720	0.66	60	1	6	1315	48	5	87	0.513
92-14	160	170	15264	0.3	1	0.1	4288	0.77	46	1	1	1734	50	5	74	0.485
92-14	170	180	15265	0.1	1	0.1	5374	0.81	41	4	1	2102	67	6	91	0.579
92-14	180	190	15266	0.1	1	0.1	3715	0.60	22	1	1	2345	56	5	52	0.400
92-14	190	200	15267	0.1	1	0.1	2661	0.43	54	1	1	1875	55	5	51	0.266
92-14	200	210	15268	0.4	1	0.1	4143	0.41	111	1	1	1966	50	5	66	0.428
92-14	210	220	15269	0.2	1	0.1	3569	0.82	22	1	1	2313	50	5	46	0.363
92-14	220	230	15270	0.1	1	0.1	3379	0.40	25	1	1	2254	53	5	47	0.369
92-14	230	240	15271	0.5	1	0.1	5535	0.49	44	1	1	2205	56	6	41	0.605
92-14	240	250	15272	0.1	1	0.1	3674	0.79	37	1	1	2310	56	6	50	0.390
92-14	250	260	15273	0.1	1	0.1	2261	0.60	11	1	1	2107	55	6	38	0.250
92-14	260	270	15274	0.1	1	0.1	3371	0.58	46	1	1	2732	57	8	59	0.360
92-14	270	280	15275	0.1	1	0.1	2173	0.29	9	1	1	2463	58	6	19	0.223
92-14	280	290	15276	0.1	1	0.1	2440	0.48	79	1	1	2550	61	7	34	0.248
92-14	290	300	15277	0.1	1	0.1	6074	0.84	4	1	1	2580	64	7	56	0.645
92-14	300	310	15278	0.9	1	0.1	2301	0.28	13	1	1	1323	38	4	41	0.244
92-14	310	320	15279	1.3	1	0.1	2302	0.51	27	1	1	1612	51	4	71	0.250
92-14	320	330	15280	0.1	1	0.1	2216	0.65	20	1	1	2803	54	7	32	0.243
92-14	330	340	15281	0.1	1	0.1	2852	0.65	57	1	1	2179	62	7	40	0.295
92-14	340	350	15282	0.1	1	0.1	2550	0.56	52	1	1	1595	53	8	44	0.262
92-14	350	360	15283	0.2	1	0.1	1672	0.40	45	2	3	1162	47	6	27	0.171
92-14	360	370	15284	1.3	1	0.1	3516	0.38	50	2	3	1617	47	7	43	0.353
92-14	370	380	15285	1.3	1	0.1	3809	0.51	68	6	2	1636	46	8	52	0.399
92-14	380	390	15286	0.9	1	0.1	2951	0.24	50	1	1	601	48	7	48	0.289

New Canamin Resources

Huckleberry

Min-En Laboratories
705 West 15th St.
North Vancouver, B.C.
Tel. (604) 980-5814

HOLE#	INTERVAL(feet)		SAMPLE	AG	AS	CD	CU	K	MO	NI	PB	TI	ZN	W	AU	CU-ASSAY
HOLE#	START	END	SAMPLE	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPB	%
92-14	390	400	15287	0.7	1	0.1	1475	0.18	40	1	1	287	41	6	26	0.137

II - 157

New Canamin Resources

Huckleberry

HOLE#	INTERVAL(feet)		SAMPLE	AG	AS	CD	CU	K	MO	NI	PB	TI	ZN	W	AU	CU-ASSAY
HOLE#	START	END	SAMPLE	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPB	%
92-15	30	40	15301	0.3	1	0.1	1121	0.39	68	1	92	1030	154	5	15	0.115
92-15	40	50	15302	0.4	1	0.1	1119	0.28	134	3	10	636	44	5	19	0.112
92-15	50	60	15303	0.7	1	0.1	1994	0.36	68	1	10	1493	50	7	46	0.207
92-15	60	70	15304	0.7	1	0.1	2301	0.37	59	1	3	1814	44	6	42	0.243
92-15	70	80	15305	1.7	1	0.1	5198	0.38	64	2	4	1586	52	8	86	0.524
92-15	80	90	15306	1.1	1	0.1	2910	0.30	93	3	2	1690	48	6	52	0.296
92-15	90	100	15307	1.1	1	0.1	3170	0.26	140	3	6	691	40	10	42	0.326
92-15	100	110	15308	0.8	1	0.1	2665	0.35	55	5	1	833	43	5	21	0.277
92-15	110	120	15309	1.0	1	0.1	3205	0.43	57	1	1	1577	42	6	78	0.333
92-15	120	130	15310	0.8	1	0.1	2621	0.35	55	1	1	1553	40	4	40	0.274
92-15	130	140	15311	1.0	1	0.1	3277	0.49	46	1	1	1696	44	8	72	0.344
92-15	140	150	15312	0.9	1	0.1	2184	0.34	69	1	1	1628	41	5	32	0.231
92-15	150	160	15313	0.9	1	0.1	2450	0.27	71	1	1	1255	41	5	49	0.249
92-15	160	170	15314	1.0	1	0.1	5254	0.49	140	7	1	1593	46	6	78	0.550
92-15	170	180	15315	1.1	1	0.1	3166	0.18	173	2	1	1040	38	6	43	0.345
92-15	180	190	15316	0.9	1	0.1	3014	0.21	55	4	2	1206	38	6	46	0.314
92-15	190	200	15317	0.8	1	0.1	2298	0.22	218	1	1	1124	36	7	52	0.249
92-15	200	210	15318	0.9	1	0.1	2400	0.21	79	2	1	1497	40	7	30	0.249
92-15	210	220	15319	0.9	1	0.1	1915	0.23	31	1	1	1413	39	9	28	0.211
92-15	220	230	15320	0.7	1	0.1	2104	0.29	132	4	2	1212	37	7	32	0.213
92-15	230	240	15321	0.4	1	0.1	1435	0.30	338	1	1	998	33	6	15	0.157
92-15	240	250	15322	0.2	1	0.1	1391	0.24	38	2	1	1367	41	6	17	0.150
92-15	250	260	15323	0.5	1	0.1	1713	0.23	32	1	1	1565	41	8	26	0.167
92-15	260	270	15324	0.6	1	0.1	1832	0.26	37	2	1	1149	37	6	24	0.191
92-15	270	280	15325	0.6	1	0.1	1711	0.20	36	1	1	1511	38	7	26	0.181
92-15	280	290	15326	0.5	1	0.1	1589	0.20	47	4	1	1340	36	7	19	0.164
92-15	290	300	15327	0.9	1	0.1	2149	0.17	77	1	1	1050	37	6	33	0.227
92-15	300	310	15328	1.7	1	0.1	4332	0.37	266	5	5	228	36	5	55	0.448
92-15	310	320	15329	0.9	1	0.1	2618	0.43	80	1	6	211	39	5	42	0.275
92-15	320	330	15330	4.0	208	0.1	3205	0.39	188	2	100	191	245	4	139	0.318
92-15	330	340	15331	0.3	1	0.1	2100	0.29	33	1	4	1383	45	7	34	0.230
92-15	340	350	15332	0.6	1	0.1	2153	0.16	32	3	1	1392	37	6	39	0.246
92-15	350	360	15333	0.1	1	0.1	2096	0.82	54	1	1	2081	41	5	39	0.229
92-15	360	370	15334	0.3	1	0.1	1834	0.17	93	2	1	873	33	4	27	0.203
92-15	370	380	15335	0.9	1	0.1	2838	0.22	102	1	1	1474	41	7	31	0.289

New Canamin Resources

Huckleberry

Min-En Laboratories
 705 West 15th St.
 North Vancouver, B.C.
 Tel. (604) 980-5814

HOLE#	INTERVAL(feet)		SAMPLE	AG	AS	CD	CU	K	MO	NI	PB	TI	ZN	W	AU	CU-ASSAY
HOLE#	START	END	SAMPLE	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPB	%
92-15	380	390	15336	0.7	1	0.1	2204	0.16	16	1	1	1147	37	4	30	0.235
92-15	390	400	15337	1.4	1	0.1	3524	0.16	21	1	1	1200	40	5	53	0.384

1533

New Canamin Resources

Huckleberry

Min-En Laboratories
705 West 15th St.
North Vancouver, B.C.
Tel. (604) 980-5814

HOLE#	INTERVAL(feet)		SAMPLE	AG	AS	CD	CU	K	MO	NI	PB	TI	ZN	W	AU	CU-ASSAY
HOLE#	START	END	SAMPLE	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPB	%
92-16	20	30	15351	1.3	1	0.1	3266	0.47	25	1	1	1631	44	5	56	0.338
92-16	30	40	15352	1.5	1	0.1	3327	0.23	40	1	1	1536	43	5	55	0.356
92-16	40	50	15353	1.4	1	0.1	4150	0.50	40	1	1	2449	52	5	81	0.439
92-16	50	60	15354	0.2	1	0.1	3652	0.75	15	1	1	3692	57	6	69	0.382
92-16	60	70	15355	0.1	1	0.1	3293	0.71	8	6	1	2494	54	8	43	0.366
92-16	70	80	15356	0.1	1	0.1	3583	0.68	13	1	1	3687	61	6	54	0.383
92-16	80	90	15357	0.1	1	0.1	2875	0.47	7	1	1	3302	57	6	79	0.328
92-16	90	100	15358	0.1	1	0.1	1494	0.54	5	1	1	2188	53	5	40	0.164
92-16	100	110	15359	0.1	1	0.1	3809	0.82	33	1	1	2920	56	5	64	0.417
92-16	110	120	15360	0.1	1	0.1	1981	0.55	10	1	1	3161	58	6	48	0.212
92-16	120	130	15361	0.1	1	0.1	1436	0.42	62	1	1	2987	51	5	43	0.147
92-16	130	140	15362	0.1	1	0.1	3654	0.43	36	1	1	3087	50	6	72	0.354
92-16	140	150	15363	0.1	1	0.1	2047	0.94	4	5	1	3623	56	10	48	0.216
92-16	150	160	15364	0.5	1	0.1	3468	0.47	86	1	1	2871	52	8	60	0.365
92-16	160	170	15365	0.1	1	0.1	1742	0.47	10	1	1	2884	45	7	27	0.186
92-16	170	180	15366	0.5	1	0.1	4460	0.39	21	1	1	2474	53	5	148	0.481
92-16	180	190	15367	0.4	1	0.1	4143	0.31	12	1	27	2608	47	5	68	0.472
92-16	190	200	15368	0.1	1	0.1	2269	0.35	49	1	1	2913	55	8	67	0.242
92-16	200	210	15369	1.3	1	0.1	5110	1.16	35	1	1	3104	61	6	61	0.540
92-16	210	220	15370	0.1	1	0.1	3304	0.48	15	1	1	2662	56	6	60	0.361
92-16	220	230	15371	0.1	1	0.1	2884	0.28	59	1	1	2659	50	6	35	0.296
92-16	230	240	15372	0.1	1	0.1	3036	0.48	36	1	1	2611	53	6	67	0.319
92-16	240	250	15373	0.1	1	0.1	2667	0.47	37	1	1	2074	54	5	63	0.297
92-16	250	260	15374	0.1	1	0.1	2979	0.32	7	1	1	2252	50	6	39	0.333
92-16	260	270	15375	0.1	1	0.1	3266	0.53	13	1	1	2344	51	5	61	0.358
92-16	270	280	15376	0.1	1	0.1	2602	0.28	10	1	1	2256	45	5	56	0.283
92-16	280	290	15377	0.1	1	0.1	2955	0.43	17	1	1	2760	54	6	52	0.326
92-16	290	300	15378	0.1	1	0.1	3032	1.20	25	1	1	2640	45	5	60	0.344

New Canamin Resources

Huckleberry

HOLE#	INTERVAL(feet)		SAMPLE	AG	AS	CD	CU	K	MO	NI	PB	TI	ZN	W	AU	CU-ASSAY
HOLE#	START	END	SAMPLE	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPB	%
92-17	60	70	15401	0.1	1	0.1	1004	0.73	28	2	1	2434	47	6	18	0.107
92-17	70	80	15402	0.9	1	0.1	3722	1.00	161	1	1	3002	52	7	50	0.395
92-17	80	90	15403	1.0	1	0.1	3776	0.89	234	1	1	2653	45	8	79	0.417
92-17	90	100	15404	1.3	1	0.1	4095	0.79	105	1	1	2415	53	8	57	0.434
92-17	100	110	15405	1.3	1	0.1	3636	0.54	62	1	1	2830	51	7	61	0.386
92-17	110	120	15406	0.3	1	0.1	3332	0.83	107	1	1	3445	50	10	40	0.359
92-17	120	130	15407	0.9	1	0.1	4829	1.05	47	3	1	3321	56	8	55	0.522
92-17	130	140	15408	3.2	1	0.1	7408	0.68	12	1	4	2508	52	8	97	0.829
92-17	140	150	15409	1.5	1	0.1	5994	0.49	103	2	1	2887	54	8	190	0.625
92-17	150	160	15410	1.3	1	0.1	5064	0.49	102	1	1	2441	47	11	73	0.551
92-17	160	170	15411	1.8	1	0.1	7657	0.76	177	8	1	2307	55	9	134	0.788
92-17	170	180	15412	0.3	1	0.1	8638	0.65	263	2	4	2172	58	11	125	0.910
92-17	180	190	15413	1.3	1	0.1	10000	0.49	193	6	8	2681	64	10	172	1.200
92-17	190	200	15414	0.1	1	0.1	5753	1.18	52	10	1	3278	59	13	141	0.591
92-17	200	210	15415	1.4	1	0.1	5651	0.63	63	5	1	1959	58	9	129	0.612
92-17	210	220	15416	2.0	1	0.1	6049	0.37	64	1	9	1903	51	10	86	0.675
92-17	220	230	15417	0.1	1	0.1	5104	1.24	63	1	1	3530	56	8	77	0.538
92-17	230	240	15418	0.6	1	0.1	8286	0.94	9	1	1	3374	69	10	147	0.386
92-17	240	250	15419	1.3	1	0.1	7263	0.78	27	1	10	3251	59	9	115	0.740
92-17	250	260	15420	0.2	1	0.1	5326	0.89	11	1	1	3530	56	9	74	0.574
92-17	260	270	15421	0.1	1	0.1	4922	0.61	311	1	1	3250	55	9	118	0.491
92-17	270	280	15422	0.1	1	0.1	5698	0.40	50	1	1	2913	59	11	97	0.620
92-17	280	290	15423	1.9	1	0.1	10000	0.49	63	6	8	2432	69	10	185	1.500
92-17	290	300	15424	0.2	1	0.1	6895	0.53	283	2	1	3068	59	12	106	0.695
92-17	300	310	15425	4.0	1	0.1	10000	0.32	131	6	15	564	53	8	157	1.080
92-17	310	320	15426	3.6	1	0.1	10000	0.30	85	9	20	288	68	9	215	1.150
92-17	320	330	15427	2.0	1	0.1	7872	0.17	81	12	11	755	63	9	128	0.804
92-17	330	340	15428	2.2	1	0.1	7122	0.14	166	10	6	363	53	7	104	0.719
92-17	340	350	15429	2.9	1	0.1	8518	0.25	128	12	6	534	56	7	105	0.825
92-17	350	360	15430	2.1	1	0.1	6222	0.10	108	19	1	533	49	9	79	0.621
92-17	360	370	15431	0.9	1	0.1	2989	0.10	81	18	1	732	45	7	66	0.303
92-17	370	380	15432	2.1	1	0.1	3813	0.17	93	10	4	1301	51	8	37	0.398
92-17	380	390	15433	1.3	1	0.1	4370	0.12	90	15	1	1428	51	7	54	0.446
92-17	390	400	15434	0.1	1	0.1	1836	0.13	42	6	9	1046	35	6	20	0.201
92-17	400	410	15435	0.2	1	0.1	1187	0.14	102	6	9	1240	31	7	5	0.124

New Canamin Resources

Huckleberry

Min-En Laboratories
 705 West 15th St.
 North Vancouver, B.C.
 Tel. (604) 980-5814

HOLE#	INTERVAL(feet)		SAMPLE	AG	AS	CD	CU	K	MO	NI	PB	TI	ZN	W	AU	CU-ASSAY
HOLE#	START	END	SAMPLE	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPB	%
92-17	410	420	15436	0.2	1	0.1	1983	0.16	31	9	9	1758	34	7	17	0.212
92-17	420	430	15437	3.2	1	0.1	6169	0.19	34	6	11	2311	48	7	32	0.624
92-17	430	440	15438	0.8	1	0.1	2893	0.14	12	7	9	2442	53	7	33	0.296
92-17	440	450	15439	1.0	1	0.1	3412	0.21	43	9	132	2737	308	7	103	0.349
92-17	450	460	15440	1.0	1	0.1	3089	0.14	15	7	24	2859	63	6	60	0.309
92-17	460	470	15441	0.6	1	0.1	3078	0.22	62	8	5	3015	45	8	59	0.313
92-17	470	480	15442	0.5	1	0.1	2257	0.17	26	6	4	3061	40	7	20	0.234
92-17	480	490	15443	0.8	1	0.1	3061	0.13	46	11	7	2995	39	6	39	0.291
92-17	490	500	15444	0.3	1	0.1	3306	0.21	16	8	12	2930	54	6	23	0.336
92-17	500	510	15445	0.1	1	0.1	2315	0.25	238	9	6	3249	44	9	29	0.227
92-17	510	520	15446	0.1	1	0.1	2238	0.26	67	7	3	2957	46	7	23	0.226
92-17	520	530	15447	0.1	1	0.1	2742	0.36	24	3	6	2952	48	6	17	0.269
92-17	530	540	15448	0.4	1	0.1	2708	0.23	22	9	5	2892	45	6	36	0.280

II-156

New Canamin Resources

Huckleberry

Min-En Laboratories
 705 West 15th St.
 North Vancouver, B.C.
 Tel. (604) 980-5814

HOLE#	INTERVAL(feet)		SAMPLE	AG	AS	CD	CU	K	MO	NI	PB	TI	ZN	W	AU	CU-ASSAY
HOLE#	START	END	SAMPLE	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPB	%
92-18	50	60	15451	0.1	1	0.1	5098	0.40	243	39	11	2569	52	6	47	0.524
92-18	60	70	15452	0.1	1	0.1	4784	0.25	39	25	8	2647	41	6	45	0.511
92-18	70	80	15453	0.6	1	0.1	9808	0.34	30	38	10	2047	68	10	104	1.080
92-18	80	90	15454	0.3	1	0.1	10000	0.24	29	18	7	2739	57	7	127	1.070
92-18	90	100	15455	0.1	1	0.1	4667	0.39	29	3	4	2828	45	7	60	0.519
92-18	100	110	15456	0.1	1	0.1	4907	0.22	31	8	3	3106	46	7	47	0.510
92-18	110	120	15457	0.7	1	0.1	6746	0.14	27	13	4	2734	49	7	67	0.700
92-18	120	130	15458	1.1	1	0.1	7335	0.15	34	10	10	1823	49	8	60	0.727
92-18	130	140	15459	0.8	1	0.1	3572	0.23	17	5	7	2068	37	8	33	0.371
92-18	140	150	15460	3.7	1	0.1	7148	0.22	28	4	6	2457	45	8	43	0.747
92-18	150	160	15461	1.2	1	0.1	5014	0.11	15	4	6	2150	45	5	59	0.523
92-18	160	170	15462	1.6	1	0.1	5991	0.14	25	10	10	1226	49	6	63	0.610
92-18	170	180	15463	0.5	1	0.1	5584	0.20	37	10	8	1651	52	7	60	0.573
92-18	180	190	15464	0.5	1	0.1	2812	0.26	38	6	12	1381	39	6	51	0.289
92-18	190	200	15465	0.7	1	0.1	4123	0.23	80	9	12	618	37	7	78	0.422
92-18	200	210	15466	0.1	1	0.1	2497	0.60	53	6	10	985	47	6	32	0.255
92-18	210	220	15467	0.4	1	0.1	3061	0.32	31	6	9	902	52	8	34	0.311
92-18	220	230	15468	0.4	1	0.1	2757	0.24	134	6	4	1657	42	10	49	0.275
92-18	230	240	15469	0.5	1	0.1	2768	0.39	52	5	7	1555	42	7	41	0.284
92-18	240	250	15470	0.1	1	0.1	2990	0.38	203	3	6	2629	42	7	38	0.305
92-18	250	260	15471	0.1	1	0.1	3144	0.29	30	3	2	2314	43	9	32	0.312
92-18	260	270	15472	0.7	1	0.1	4808	0.23	184	12	7	2175	47	7	63	0.517
92-18	270	280	15473	0.1	1	0.1	3175	0.23	18	9	2	2836	43	10	75	0.325
92-18	280	290	15474	0.5	1	0.1	4438	0.19	31	13	6	2335	39	7	61	0.483
92-18	290	300	15475	0.1	1	0.1	2097	0.38	58	8	7	1681	39	7	34	0.231
92-18	300	310	15476	0.1	1	0.1	3482	1.43	95	33	1	3240	52	11	54	0.371
92-18	310	320	15477	0.2	1	0.1	1277	0.32	50	6	3	1605	27	7	50	0.131
92-18	320	330	15478	0.1	1	0.1	1344	0.32	74	8	6	824	33	6	18	0.142

157

New Canamin Resources

Huckleberry

Min-En Laboratories
 705 West 15th St.
 North Vancouver, B.C.
 Tel. (604) 980-5814

HOLE#	INTERVAL(feet)		SAMPLE	AG	AS	CD	CU	K	MO	NI	PB	TI	ZN	W	AU	CU-ASSAY
HOLE#	START	END	SAMPLE	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPB	%
92-19	30	40	15501	0.1	1	0.1	2188	0.40	33	1	1	2259	37	6	26	0.229
92-19	40	50	15502	0.3	1	0.1	3011	0.51	84	1	1	2657	43	7	44	0.296
92-19	50	60	15503	0.6	1	0.1	3688	0.63	53	1	1	3070	44	10	59	0.386
92-19	60	70	15504	1.3	1	0.1	4726	0.68	59	1	5	2868	43	7	38	0.498
92-19	70	80	15505	0.7	1	0.1	2443	0.83	123	1	1	2533	41	6	34	0.251
92-19	80	90	15506	0.3	1	0.1	2982	0.42	47	1	5	1612	40	7	39	0.306
92-19	90	100	15507	0.1	1	0.1	3306	0.44	64	1	3	1574	40	9	40	0.340
92-19	100	110	15508	0.1	1	0.1	1677	0.69	49	1	2	2453	36	6	20	0.180
92-19	110	120	15509	0.1	1	0.1	2695	0.43	46	1	4	2216	39	6	40	0.289
92-19	120	130	15510	0.2	1	0.1	1917	0.29	81	1	1	2307	37	9	24	0.207
92-19	130	140	15511	0.1	1	0.1	1727	0.52	46	1	2	2668	39	10	27	0.181
92-19	140	150	15512	0.1	1	0.1	2098	0.53	51	1	2	2511	40	8	38	0.218
92-19	150	160	15513	0.1	1	0.1	1526	0.46	25	1	3	2081	38	7	30	0.158
92-19	160	170	15514	0.1	1	0.1	1721	0.64	36	1	1	2413	42	8	25	0.175
92-19	170	180	15515	0.1	1	0.1	2346	0.69	53	1	4	2091	40	9	26	0.248
92-19	180	190	15516	0.1	1	0.1	3021	0.84	59	1	2	2155	44	6	34	0.311
92-19	190	200	15517	0.1	1	0.1	4778	0.46	52	7	6	1939	45	7	48	0.506
92-19	200	210	15518	0.1	1	0.1	5014	0.35	58	12	8	1143	50	6	53	0.547
92-19	210	220	15519	0.3	1	0.1	2498	0.31	48	6	7	905	37	7	33	0.262
92-19	220	230	15520	0.1	1	0.1	1427	0.35	68	3	5	1276	35	5	40	0.158
92-19	230	240	15521	0.1	1	0.1	3397	0.80	46	1	1	2109	53	6	34	0.372
92-19	240	250	15522	0.1	1	0.1	2831	0.65	55	1	3	2566	52	7	37	0.275
92-19	250	260	15523	0.1	1	0.1	2476	0.53	25	1	1	2602	45	7	18	0.266
92-19	260	270	15524	0.1	1	0.1	3014	0.76	36	1	2	2847	47	7	32	0.333
92-19	270	280	15525	0.1	1	0.1	1876	0.54	40	1	8	2396	54	6	21	0.210
92-19	280	290	15526	0.1	1	0.1	3259	0.31	8	3	6	2635	41	7	49	0.337
92-19	290	300	15527	0.1	1	0.1	2381	0.72	186	1	1	2994	49	7	53	0.247
92-19	300	310	15528	0.1	1	0.1	1630	0.44	137	4	4	1833	49	8	18	0.162
92-19	310	320	15529	0.1	1	0.1	1504	0.31	26	8	8	1471	40	7	24	0.155
92-19	320	330	15530	0.3	1	0.1	2978	0.45	39	30	4	2171	44	10	33	0.302
92-19	330	340	15531	0.1	1	0.1	1981	0.59	16	32	5	2048	43	11	35	0.207
92-19	340	350	15532	0.2	1	0.1	712	0.25	11	7	7	955	30	8	12	0.076
92-19	350	360	15533	0.2	1	0.1	2165	0.44	96	5	5	2057	46	7	30	0.218
92-19	360	370	15534	0.1	1	0.1	1303	0.67	38	10	5	2005	45	7	23	0.129
92-19	370	380	15535	0.6	1	0.1	1376	0.18	24	4	10	991	31	5	16	0.147

II-156

New Canamin Resources

Huckleberry

Min-En Laboratories
 705 West 15th St.
 North Vancouver, B.C.
 Tel. (604) 980-5814

HOLE#	INTERVAL(feet)		SAMPLE	AG	AS	CD	CU	K	MO	NI	PB	TI	ZN	W	AU	CU-ASSAY
HOLE#	START	END	SAMPLE	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPB	%
92-19	380	390	15536	0.1	1	0.1	728	0.31	14	35	13	743	53	5	9	0.077
92-19	390	395	15537	0.1	1	0.1	742	0.18	16	2	7	359	33	6	14	0.077

6-51-11

New Canamin Resources

Huckleberry

 Min-En Laboratories
 705 West 15th St.
 North Vancouver, B.C.
 Tel. (604) 980-5814

HOLE#	INTERVAL(feet)		SAMPLE	AG	AS	CD	CU	K	MO	NI	PB	TI	ZN	W	AU	CU-ASSAY
HOLE#	START	END	SAMPLE	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPB	%
92-20	40	50	15551	0.1	1	0.1	2858	0.25	4	1	3	1818	42	5	21	0.311
92-20	50	60	15552	0.2	1	0.1	4777	0.28	81	1	7	1901	47	4	71	0.561
92-20	60	70	15553	0.7	1	0.1	2690	0.25	36	1	4	1408	34	5	36	0.296
92-20	70	80	15554	0.4	1	0.1	2709	0.39	112	1	4	1261	37	4	29	0.293
92-20	80	90	15555	0.1	1	0.1	1606	0.25	45	1	6	564	32	3	31	0.160
92-20	90	100	15556	0.1	1	0.1	2359	0.22	35	1	7	634	32	3	35	0.265
92-20	100	110	15557	0.6	1	0.1	4815	0.33	65	1	7	766	37	3	68	0.539
92-20	110	120	15558	0.6	1	0.1	2995	0.37	206	1	166	1436	37	5	38	0.329
92-20	120	130	15559	0.9	1	0.1	3465	0.79	41	1	2	2220	41	4	32	0.390
92-20	130	140	15560	0.7	1	0.1	4060	0.75	16	1	3	2102	41	5	44	0.484
92-20	140	150	15561	0.4	1	0.1	2403	1.06	24	1	1	2522	38	4	27	0.263
92-20	150	160	15562	0.5	1	0.1	2606	1.10	164	1	1	2627	39	5	42	0.285
92-20	160	170	15563	0.1	1	0.1	3355	0.57	46	1	5	1396	41	4	45	0.377
92-20	170	180	15564	0.1	1	0.1	2546	0.86	164	1	3	2084	41	6	46	0.267
92-20	180	190	15565	0.1	1	0.1	3535	0.83	286	1	2	1994	42	4	49	0.382
92-20	190	200	15566	0.9	1	0.1	4070	0.73	48	1	6	1450	42	4	56	0.459
92-20	200	210	15567	1.5	1	0.1	4576	0.41	147	2	9	884	40	3	69	0.524
92-20	210	220	15568	0.7	1	0.1	3288	0.51	34	1	2	1906	39	6	60	0.356
92-20	220	230	15569	0.8	1	0.1	2411	0.40	16	1	4	1792	34	4	33	0.260
92-20	230	240	15570	0.2	1	0.1	2080	0.51	69	1	2	1884	35	5	34	0.220
92-20	240	250	15571	0.1	1	0.1	3324	0.83	26	1	7	1883	46	4	59	0.370
92-20	250	260	15572	0.1	1	0.1	5767	1.11	91	4	3	2762	51	6	79	0.615
92-20	260	270	15573	0.1	1	0.1	2827	1.10	56	1	1	2490	51	6	58	0.312
92-20	270	280	15574	0.1	1	0.1	7389	0.60	177	8	8	1775	57	6	98	0.813
92-20	280	290	15575	1.1	1	0.1	9455	0.34	168	16	15	2773	57	7	100	0.920
92-20	290	300	15576	0.4	1	0.1	7602	0.22	90	12	15	2532	70	6	91	0.741
92-20	300	310	15577	0.1	1	0.1	2584	0.37	191	3	2	1260	44	5	28	0.252
92-20	310	320	15578	0.1	1	0.1	2262	0.59	37	6	3	1460	45	6	27	0.233
92-20	320	330	15579	0.1	1	0.1	3076	0.56	25	11	14	1547	50	4	30	0.317
92-20	330	340	15580	0.1	1	0.1	4873	0.32	26	34	5	2111	50	6	76	0.512
92-20	340	350	15581	0.1	1	0.1	3194	0.32	2	17	7	2391	45	5	78	0.329
92-20	350	360	15582	0.1	1	0.1	2998	0.31	108	5	12	2547	45	6	35	0.309
92-20	360	370	15583	0.1	1	0.1	3347	0.25	16	7	6	3123	39	7	42	0.335
92-20	370	380	15584	0.1	1	0.1	4136	0.43	34	11	6	3096	50	7	53	0.418
92-20	380	390	15585	0.1	1	0.1	3898	0.29	50	8	9	3013	49	7	40	0.396

New Canamin Resources

Huckleberry

Min-En Laboratories
 705 West 15th St.
 North Vancouver, B.C.
 Tel. (604) 980-5814

HOLE#	INTERVAL(feet)		SAMPLE	AG	AS	CD	CU	K	MO	NI	PB	TI	ZN	W	AU	CU-ASSAY
HOLE#	START	END	SAMPLE	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPB	%
92-20	390	400	15586	0.1	1	0.1	1781	0.44	38	8	8	1205	31	7	21	0.184
92-20	400	410	15587	0.1	1	0.1	4772	0.32	27	56	10	1606	59	7	90	0.502
92-20	410	416	15588	0.1	1	0.1	82	0.22	1	187	1	2312	78	7	8	0.008

191-11

New Canamin Resources

Huckleberry

Min-En Laboratories
 705 West 15th St.
 North Vancouver, B.C.
 Tel. (604) 980-5814

HOLE#	INTERVAL(feet)		SAMPLE	AG	AS	CD	CU	K	MO	NI	PB	TI	ZN	W	AU	CU-ASSAY
HOLE#	START	END	SAMPLE	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPB	%
92-21	30	40	15601	0.1	1	0.1	2518	0.16	44	5	6	1145	45	7	31	0.258
92-21	40	50	15602	0.4	1	0.1	4230	0.12	34	4	12	1306	46	8	58	0.441
92-21	50	60	15603	0.3	1	0.1	4590	0.20	13	4	10	1585	45	5	56	0.464
92-21	60	70	15604	0.1	1	0.1	2514	0.13	28	4	10	1027	44	5	61	0.263
92-21	70	80	15605	0.1	1	0.1	3408	0.17	20	5	9	531	45	5	33	0.353
92-21	80	90	15606	0.1	1	0.1	3159	0.14	39	5	6	983	50	8	22	0.301
92-21	90	100	15607	0.1	1	0.1	1819	0.16	85	4	10	1059	43	7	20	0.194
92-21	100	110	15608	0.1	1	0.1	2278	0.16	33	6	9	1151	45	6	31	0.236
92-21	110	120	15609	0.1	1	0.1	1885	0.21	29	6	8	1481	47	5	29	0.203
92-21	120	130	15610	0.1	1	0.1	2356	0.23	67	4	7	1811	50	6	24	0.240
92-21	130	135	15611	0.1	1	0.1	3317	0.40	15	1	3	2447	47	5	52	0.347

29/- II

New Canamin Resources

Huckleberry

Min-En Laboratories
 705 West 15th St.
 North Vancouver, B.C.
 Tel. (604) 980-5814

HOLE#	INTERVAL(feet)		SAMPLE	AG	AS	CD	CU	K	MO	NI	PB	TI	ZN	W	AU	CU-ASSAY
HOLE#	START	END	SAMPLE	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPB	%
92-21V	20	30	15651	0.1	1	0.1	1499	0.19	15	6	7	913	56	5	14	0.161
92-21V	30	40	15652	0.1	1	0.1	2722	0.18	180	5	11	729	49	6	23	0.272
92-21V	40	50	15653	0.1	1	0.1	2564	0.15	40	8	7	1079	47	7	25	0.264
92-21V	50	60	15654	0.1	1	0.1	2496	0.10	43	3	11	989	50	7	13	0.268
92-21V	60	70	15655	0.1	1	0.1	2593	0.09	26	3	6	1034	49	5	40	0.262
92-21V	70	80	15656	0.1	1	0.1	2985	0.13	23	5	8	984	47	6	39	0.294
92-21V	80	90	15657	0.3	1	0.1	3167	0.09	53	7	6	922	43	5	55	0.331
92-21V	90	100	15658	0.1	1	0.1	2768	0.11	52	5	8	752	43	5	36	0.298
92-21V	100	110	15659	0.1	1	0.1	2551	0.15	24	7	6	619	47	6	21	0.252
92-21V	110	120	15660	0.1	1	0.1	2486	0.15	46	5	6	694	44	6	35	0.262
92-21V	120	130	15661	0.2	1	0.1	3490	0.16	56	6	8	628	49	7	49	0.360
92-21V	130	140	15662	0.3	1	0.1	3157	0.12	106	9	8	876	47	6	38	0.324
92-21V	140	150	15663	0.1	1	0.1	1952	0.09	20	7	8	1316	44	7	17	0.194
92-21V	150	160	15664	0.1	1	0.1	2008	0.08	50	6	8	1084	41	5	25	0.209
92-21V	160	170	15665	0.1	1	0.1	2132	0.08	35	9	8	855	45	7	33	0.222
92-21V	170	180	15666	0.7	1	0.1	3813	0.10	190	5	7	1135	47	6	17	0.388
92-21V	180	190	15667	0.1	1	0.1	2031	0.07	16	6	7	1287	41	5	26	0.206
92-21V	190	200	15668	1.0	1	0.1	3482	0.09	34	7	12	1001	43	6	39	0.366
92-21V	200	210	15669	0.5	1	0.1	2851	0.09	60	8	7	704	42	5	30	0.296
92-21V	210	220	15670	0.1	1	0.1	1539	0.06	81	7	8	1045	37	5	42	0.160

II-163

New Canamin Resources

Huckleberry

Min-En Laboratories
705 West 15th St.
North Vancouver, B.C.
Tel. (604) 980-5814

HOLE#	INTERVAL(feet)		SAMPLE	AG	AS	CD	CU	K	MO	NI	PB	TI	ZN	W	AU	CU-ASSAY
HOLE#	START	END	SAMPLE	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPB	%
92-22	44	50	15701	0.1	1	0.1	4052	0.77	5	1	4	1575	54	4	39	0.458
92-22	50	60	15702	0.1	1	0.1	3403	0.86	16	1	1	1705	44	4	40	0.361
92-22	60	70	15703	0.1	1	0.1	1718	0.67	17	1	3	1691	34	4	25	0.191
92-22	70	80	15704	0.2	1	0.1	1684	0.44	18	1	5	769	29	3	31	0.172
92-22	80	90	15705	0.5	1	0.1	1525	0.24	59	1	8	161	26	3	28	0.167
92-22	90	100	15706	0.3	1	0.1	1369	0.31	26	1	7	369	28	3	17	0.161
92-22	100	110	15707	0.4	1	0.1	928	0.18	31	1	3	187	28	3	16	0.107
92-22	110	120	15708	0.3	1	0.1	859	0.20	75	1	6	157	27	2	7	0.092
92-22	120	130	15709	0.1	1	0.1	823	0.30	97	1	4	269	24	3	15	0.093
92-22	130	140	15710	0.1	1	0.1	1502	0.54	89	1	7	694	30	3	17	0.162
92-22	140	150	15711	0.1	1	0.1	3144	0.89	47	1	3	1396	37	4	29	0.362
92-22	150	160	15712	0.1	1	0.1	2224	0.87	51	1	1	1374	31	4	27	0.235
92-22	160	170	15713	0.1	1	0.1	1837	0.54	104	1	3	873	32	5	21	0.199
92-22	170	180	15714	0.9	1	0.1	4811	0.68	57	1	5	1130	37	4	40	0.535
92-22	180	190	15715	1.3	1	0.1	5135	0.71	35	1	1	1711	35	4	47	0.618
92-22	190	200	15716	1.3	1	0.1	3355	0.51	90	1	1	1954	32	4	41	0.363
92-22	200	210	15717	1.3	1	0.1	3899	0.49	82	1	1	1731	34	5	38	0.440
92-22	210	220	15718	3.7	1	0.1	9052	0.42	108	1	11	1234	39	4	36	1.020
92-22	220	230	15719	0.2	1	0.1	4781	0.97	157	1	1	2464	42	5	60	0.550
92-22	230	240	15720	2.0	1	0.1	7222	0.80	100	1	4	2244	43	5	47	0.830
92-22	240	250	15721	0.1	1	0.1	3351	0.99	26	1	1	2494	40	5	41	0.394
92-22	250	260	15722	0.2	1	0.1	3188	0.86	48	1	1	2087	38	4	39	0.371
92-22	260	270	15723	0.1	1	0.1	3922	0.82	87	1	1	1730	41	5	39	0.452
92-22	270	280	15724	0.7	1	0.1	3390	0.54	25	1	1	1366	35	4	39	0.416
92-22	280	290	15725	1.3	1	0.1	4876	0.40	83	1	1	878	37	5	33	0.543
92-22	290	300	15726	0.9	1	0.1	2935	0.33	53	1	1	929	35	4	27	0.327
92-22	300	310	15727	0.9	1	0.1	4205	0.31	167	1	5	1062	41	4	46	0.454
92-22	310	320	15728	0.8	1	0.1	3678	0.19	252	3	7	199	26	4	32	0.389
92-22	320	330	15729	0.1	1	0.1	2835	0.23	171	1	3	1140	29	5	26	0.294
92-22	330	340	15730	0.1	1	0.1	1954	0.32	102	1	4	1194	29	4	16	0.207
92-22	340	350	15731	0.2	1	0.1	2839	0.37	160	1	5	1014	34	5	25	0.291
92-22	350	360	15732	0.1	1	0.1	3566	0.45	83	1	4	1631	37	5	34	0.355
92-22	360	370	15733	0.1	1	0.1	1847	0.28	73	1	2	1045	24	4	35	0.189
92-22	370	380	15734	0.1	1	0.1	3824	0.27	89	1	7	529	34	5	34	0.382
92-22	380	390	15735	0.1	1	0.1	2525	0.27	81	1	3	795	34	6	26	0.263

New Canamin Resources

Huckleberry

Min-En Laboratories
 705 West 15th St.
 North Vancouver, B.C.
 Tel. (604) 980-5814

HOLE#	INTERVAL(feet)		SAMPLE	AG	AS	CD	CU	K	MO	NI	PB	TI	ZN	W	AU	CU-ASSAY
HOLE#	START	END	SAMPLE	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPB	%
92-22	390	400	15736	0.1	1	0.1	2728	0.32	131	1	5	991	33	5	30	0.296
92-22	400	410	15737	0.1	1	0.1	3674	0.31	85	1	3	1118	38	7	35	0.355
92-22	410	420	15738	0.2	1	0.1	3203	0.36	75	1	6	1093	35	5	31	0.352
92-22	420	430	15739	0.7	1	0.1	4843	0.33	163	1	12	787	39	6	44	0.476
92-22	430	440	15740	0.9	1	0.1	4507	0.19	179	1	9	1293	39	5	41	0.474
92-22	440	450	15741	0.2	1	0.1	2966	0.34	139	1	3	1694	35	7	31	0.314

11-165

CAMP: NEW CANNON RESOURCES LTD.

PROJ: WICKLEBERRY

ATTN: B AINSWORTH/A SAVAGE/D JENKINS

MIN-EM LABS — ICP REPORT

705 WEST 15TH ST., NORTH VANCOUVER, B.C. V7M 1T2
(604)980-5814 OR (604)988-4524

FILE NO: 35-0031-RJ1

DATE: 93/03/10

* CORE * (ACT:F31)

SAMPLE NUMBER	AG PPM	AL %	AS PPM	B PPM	BA PPM	BE PPM	BI PPM	CA %	CD PPM	CO PPM	CU PPM	FE %	K %	LI PPM	MG %	MN PPM	MO PPM	NA %	NI PPM	P PPM	PB PPM	SB PPM	SR PPM	TM PPM	Tl PPM	V PPM	ZN PPM	GA PPM	SH PPM	W PPM	CR PPM	
932801	.1	2.78	1	9	489	.2	11	.99	.1	31	194	7.36	.79	8	2.02	362	1	.20	2	670	1	10	51	11	1232	256.6	26	11	2	11	71	

COMP: NEW KAMMIN RESOURCES LTD.
 PROJ: HUCKLEBERRY
 ATTN: B AINSWORTH/A SAVAGE/D JENKINS

MIN-EM LABS — ICP REPORT
 705 WEST 15TH ST., NORTH VANCOUVER, B.C. V7M 1B2
 (604)980-5814 OR (604)988-4524

FILE NO: 35-0028-R
 DATE: 93/03/
 * CORE * (ACT:F3)

SAMPLE NUMBER	AG PPM	AL %	AS PPM	B PPM	BA PPM	BE PPM	BI PPM	CA %	CD PPM	CO PPM	CU PPM	FE %	K %	LI PPM	MG %	NI PPM	NO PPM	NA %	NE PPM	P PPM	PB PPM	SE PPM	SR PPM	TM PPM	TI PPM	V PPM	ZN PPM	GA PPM	SH PPM	U PPM	CR PPM
932701	.1	2.15	1	6	247	.1	13	1.30	.1	26	65	5.61	.33	4	.97	256	1	.30	1	950	1	11	86	6	989	172.1	24	8	4	9	64
932702	.1	3.08	1	8	453	.1	12	1.59	.1	24	127	6.24	.48	4	1.28	295	2	.40	1	850	3	12	103	10	1002	201.3	23	10	4	11	105
932703	.1	2.32	1	7	95	.1	12	1.34	.1	24	250	6.25	.22	6	1.30	370	1	.26	1	800	1	11	64	9	1283	196.7	29	9	3	10	67
932704	.1	2.63	1	9	131	.1	10	1.67	.1	21	223	7.36	.31	6	1.29	609	1	.31	1	840	1	9	71	8	1102	233.2	28	10	2	10	76
932705	.1	2.63	1	9	213	.1	10	1.41	.1	19	84	6.75	.35	5	1.23	335	1	.38	1	990	1	10	70	8	1144	213.8	25	10	11	10	81
932706	.1	2.62	1	9	418	.1	11	1.50	.1	37	97	6.39	.57	6	1.48	309	1	.24	1	820	3	9	81	8	1113	205.5	26	10	3	9	61
932707	.3	2.66	1	9	316	.2	7	2.38	.1	29	47	5.24	.37	6	1.27	368	1	.20	1	850	2	9	93	9	665	157.7	25	9	2	7	44
932708	.2	2.69	1	10	355	.2	11	1.72	.1	34	58	5.16	.47	5	1.19	388	1	.28	1	890	5	10	98	8	794	157.7	37	9	2	7	51

II
 91-187

MAR 15 1993 11:53 SOUTHERN GOLD RESOURCES N. VAN.
 03/10/1993 13:57 MIN-EM VAN.
 604 980 9621 P.03 P.7

COMP: NEW CANADIAN RESOURCES LTD.
 PROJ: HUCKLEBERRY
 ATTN: B AINSWORTH/A SAVAGE/O JENKINS

MIM-EN LABS — ICP REPORT
 705 WEST 15TH ST., NORTH VANCOUVER, B.C. V7N 1T2
 (604)980-5814 OR (604)988-4526

FILE NO: 36-0030-R
 DATE: 93/03/
 * CORE * (ACT:F3)

SAMPLE NUMBER	AG PPM	AL %	AS PPM	B PPM	BA PPM	BE PPM	BI PPM	CA %	CD PPM	CO PPM	CJ PPM	FE %	K %	LI PPM	MG %	MN PPM	MO PPM	NA %	NI PPM	P PPM	PR PPM	SB PPM	SR PPM	TH PPM	TI PPM	V PPM	ZN PPM	GA PPM	SM PPM	U PPM	CR PPM
932301	1.1	1.18	1	5	325	.3	7	1.20	.1	22	466	2.65	.40	7	.76	631	10	.05	8	550	1	7	25	6	238	40.5	31	4	1	6	71
932302	1.0	1.77	1	7	474	.2	18	1.09	.3	40	1000	5.34	.68	13	1.25	581	7	.08	4	620	1	9	31	8	869	128.7	30	7	1	10	97
932303	1.0	1.76	1	6	375	.2	8	1.66	.4	29	557	3.86	.74	14	1.49	560	21	.07	6	710	1	7	46	9	926	114.7	32	7	1	8	65
932304	1.2	2.31	1	8	344	.2	10	2.24	.1	23	415	3.90	.70	15	1.29	360	3	.18	6	1150	1	9	73	9	1040	95.8	23	8	1	7	71
932305	1.6	1.81	1	6	336	.2	17	1.93	.1	28	604	3.82	.62	18	1.10	511	5	.14	3	840	1	8	59	8	985	79.0	28	7	1	8	80
932306	1.4	1.46	1	6	410	.3	7	1.89	.1	24	798	3.05	.65	11	.97	339	6	.11	3	730	1	7	65	8	645	60.3	23	5	1	7	48
932307	1.0	.99	1	4	255	.2	5	1.33	.1	25	787	3.28	.35	10	.84	372	19	.05	5	540	1	6	34	6	284	52.9	26	5	1	5	72
932308	.8	1.22	1	5	205	.2	7	1.33	.1	26	458	3.92	.47	12	1.04	430	43	.07	1	650	1	7	38	7	648	73.2	26	6	1	6	55
932309	.9	1.84	1	6	228	.1	9	1.53	.1	26	757	4.70	.75	17	1.54	377	3	.11	1	970	1	9	47	8	1052	115.3	24	8	2	8	79

691-#

MGR: 15/93 11:51 AM SOUTHERN GOLD RESOURCES N. VAN.

604 980 9621 P.07

P.3

I.C.P., Au - fire geochem and Cu-assay

New Canamin Resources

Huckleberry

Min-En Laboratories
705 West 15th St.
North Vancouver, B.C.
Tel. (604) 980-5814

II-170

HOLE#	INTERVAL(feet)	SAMPL	AG	AS	CD	CU	K	MO	NI	PB	TI	ZN	W	AU	CU-ASSAY	
HOLE#	START	END	SAMPL	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPB	%	
92-18V	40	50	15751	0.1	1	0.1	5647	0.52	88	1	2	2124	53	6	63	0.636
92-18V	50	60	15752	0.9	1	0.1	10000	0.63	139	3	67	2059	210	14	83	1.120
92-18V	60	70	15753	2.1	1	0.1	9212	0.13	75	3	18	1663	59	6	132	1.000
92-18V	70	80	15754	1.4	1	0.1	8837	0.15	58	18	5	2118	59	7	95	0.920
92-18V	80	90	15755	9.3	1	0.1	10000	0.23	87	18	16	1832	73	8	280	1.670
92-18V	90	100	15756	1.1	1	0.1	7316	0.23	39	13	7	2933	45	8	75	0.802
92-18V	100	110	15757	0.2	1	0.1	5397	0.15	127	11	7	2636	46	7	43	0.595
92-18V	110	120	15758	0.3	1	0.1	6673	0.14	93	19	8	2225	55	7	75	0.706
92-18V	120	130	15759	0.1	1	0.1	6072	0.14	45	22	6	2524	55	7	57	0.647
92-18V	130	140	15760	2.4	1	0.1	8363	0.15	58	23	8	1933	54	8	47	0.900
92-18V	140	150	15761	3.2	1	0.1	10000	0.26	123	21	7	2299	59	8	97	1.110
92-18V	150	160	15762	0.5	1	0.1	2753	0.33	39	10	4	2548	43	7	30	0.284
92-18V	160	170	15763	0.8	1	0.1	3671	0.43	70	8	2	2176	48	5	34	0.393
92-18V	170	180	15764	1.6	1	0.1	5283	0.34	35	16	3	2547	51	10	37	0.563
92-18V	180	190	15765	0.6	1	0.1	5846	0.41	64	18	9	1596	50	7	61	0.634
92-18V	190	200	15766	1.0	1	0.1	4270	0.38	9	29	2	1439	44	8	63	0.472
92-18V	200	210	15767	0.1	1	0.1	3594	0.57	73	22	6	2012	54	8	75	0.391
92-18V	210	220	15768	1.0	1	0.1	3889	0.14	122	14	8	2213	42	8	50	0.417
92-18V	220	230	15769	0.1	1	0.1	3684	0.42	8	18	7	2090	42	8	44	0.408
92-18V	230	240	15770	1.5	1	0.1	7647	0.52	66	12	8	2952	58	9	61	0.805
92-18V	240	250	15771	0.6	1	0.1	5013	0.27	105	11	9	1941	44	6	56	0.562
92-18V	250	260	15772	1.6	1	0.1	6208	0.16	21	11	13	1735	48	8	61	0.675
92-18V	260	270	15773	1.6	1	0.1	6658	0.18	22	10	13	2158	53	6	92	0.736
92-18V	270	280	15774	1.6	1	0.1	5363	0.14	42	9	11	1747	43	9	69	0.574
92-18V	280	290	15775	1.3	1	0.1	4984	0.16	76	10	53	1334	116	8	40	0.576
92-18V	290	300	15776	0.1	1	0.1	4089	0.37	43	6	5	1768	40	8	62	0.464
92-18V	300	310	15777	1.5	1	0.1	5663	0.25	22	10	9	1824	43	6	72	0.618
92-18V	310	320	15778	0.1	1	0.1	2804	0.76	108	5	1	2987	45	8	36	0.295
92-18V	320	330	15779	1.7	1	0.1	5895	0.18	35	9	9	2811	49	8	46	0.631
92-18V	330	340	15780	0.1	1	0.1	5538	0.50	35	23	7	2710	53	10	45	0.601
92-18V	340	350	15781	1.5	1	0.1	8762	0.29	29	27	10	2579	56	9	98	0.900
92-18V	350	360	15782	0.7	1	0.1	8808	0.43	30	26	9	2838	64	10	109	0.910
92-18V	360	370	15783	0.1	1	0.1	6123	0.56	43	13	5	2084	61	7	73	0.639
92-18V	370	380	15784	1.1	1	0.1	6173	0.21	37	26	15	1345	68	8	66	0.665
92-18V	380	390	15785	1.7	1	0.1	7491	0.08	9	50	13	732	56	5	91	0.870
92-18V	390	400	15786	1.6	1	0.1	6573	0.15	26	68	13	588	65	7	85	0.762

I.C.P., Au - fire geochem and Cu-assay

New Canamin Resources

Huckleberry

Min-En Laboratories
705 West 15th St.
North Vancouver, B.C.
Tel. (604) 980-5814

II-171

HOLE#	INTERVAL(feet)		SAMPL	AG	AS	CD	CU	K	MO	NI	PB	TI	ZN	W	AU	CU-ASSAY
HOLE#	START	END	SAMPL	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPB	%
92-23	40	50	15801	3.4	1	0.1	7841	0.63	89	12	16	2071	46	7	96	0.860
92-23	50	60	15802	2.0	1	0.1	6133	0.55	98	2	13	1960	41	7	93	0.700
92-23	60	70	15803	2.7	1	0.1	7911	0.66	111	2	17	2321	42	6	93	0.870
92-23	70	80	15804	1.9	1	0.1	8513	1.41	64	11	19	3078	52	8	106	0.950
92-23	80	90	15805	1.4	1	0.1	8762	1.46	71	26	19	3258	67	13	84	0.940
92-23	90	100	15806	0.1	1	0.1	3108	1.15	15	18	15	2562	47	12	24	0.311
92-23	100	110	15807	1.1	1	0.1	6162	0.92	14	12	16	2587	58	10	79	0.666
92-23	110	120	15808	0.7	1	0.1	3680	1.06	56	1	12	2768	40	8	48	0.413
92-23	120	130	15809	3.2	1	0.1	9426	0.38	93	16	20	1617	48	8	144	1.040
92-23	130	140	15810	1.8	1	0.1	4776	0.22	257	14	15	842	44	8	67	0.519
92-23	140	150	15811	1.0	1	0.1	2774	0.18	130	7	13	1358	41	8	62	0.311
92-23	150	160	15812	1.1	1	0.1	2500	0.20	178	8	15	604	38	8	51	0.271
92-23	160	170	15813	0.9	1	0.1	2287	0.16	52	3	13	1249	40	8	75	0.260
92-23	170	180	15814	0.6	1	0.1	2332	0.16	105	8	14	1490	46	7	46	0.233
92-23	180	190	15815	0.9	1	0.1	2757	0.12	185	5	21	1022	39	7	30	0.297
92-23	190	200	15816	1.0	1	0.1	3139	0.06	62	7	15	1013	39	7	34	0.353
92-23	200	210	15817	2.4	1	0.1	5594	0.10	461	8	22	681	43	7	49	0.614
92-23	210	220	15818	3.6	1	0.1	7019	0.10	695	8	26	482	45	7	117	0.785
92-23	220	230	15819	0.4	1	0.1	3099	0.16	329	3	16	702	42	8	92	0.340
92-23	230	240	15820	0.7	1	0.1	3133	0.27	266	2	13	1326	39	7	37	0.351
92-23	240	250	15821	2.3	1	0.1	4124	0.18	91	4	15	1151	33	10	56	0.483
92-23	250	260	15822	1.1	1	0.1	3160	0.28	165	1	14	1778	36	6	91	0.350
92-23	260	270	15823	0.4	1	0.1	3995	0.44	593	2	13	1827	38	8	64	0.418
92-23	270	280	15824	2.0	1	0.1	6492	0.29	123	3	23	1483	39	7	68	0.709
92-23	280	290	15825	0.6	1	0.1	3957	0.19	108	3	17	1241	35	7	52	0.440
92-23	290	300	15826	0.1	1	0.1	2908	0.10	40	1	16	843	39	8	43	0.335
92-23	300	310	15827	0.1	1	0.1	3755	0.09	98	1	18	663	33	6	47	0.437
92-23	310	320	15828	0.1	1	0.1	2209	0.12	13	2	14	762	33	7	36	0.258
92-23	320	330	15829	0.1	1	0.1	2555	0.13	18	1	15	974	37	7	35	0.286
92-23	330	340	15830	0.6	1	0.1	5404	0.17	47	6	17	1212	47	7	71	0.642
92-23	340	350	15831	0.1	1	0.1	4467	0.33	34	4	19	1613	44	8	58	0.490
92-23	350	360	15832	1.0	1	0.1	6553	0.16	108	6	19	981	52	7	100	0.756
92-23	360	370	15833	0.9	1	0.1	6628	0.16	48	23	23	887	51	6	88	0.795
92-23	370	380	15834	1.7	1	0.1	8134	0.22	46	44	21	873	56	7	109	0.850
92-23	380	390	15835	3.2	1	0.1	8338	0.19	81	35	20	1251	56	7	53	0.880
92-23	390	400	15836	0.1	1	0.1	5906	0.54	89	18	24	1747	58	8	49	0.676

I.C.P., Au - fire geochem and Cu-assay

New Canamin Resources

Huckleberry

Min-En Laboratories
705 West 15th St.
North Vancouver, B.C.
Tel. (604) 980-5814

HOLE#	INTERVAL(feet)		SAMPL	AG	AS	CD	CU	K	MO	NI	PB	TI	ZN	W	AU	CU-ASSAY
HOLE#	START	END	SAMPL	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPB	%
92-23	400	410	15837	0.1	1	0.1	5486	0.31	81	1	16	1466	62	9	41	0.596
92-23	410	420	15838	2.3	1	0.1	10000	0.32	45	31	21	2073	72	13	56	1.480
92-23	420	430	15839	0.1	1	0.1	5566	0.32	51	14	20	2257	48	8	128	0.564
92-23	430	440	15840	1.4	1	0.1	7682	0.33	29	26	32	1581	58	8	76	0.851
92-23	440	450	15841	0.1	1	0.1	3849	0.56	65	25	25	1634	53	7	56	0.434
92-23	450	460	15842	0.1	1	0.1	4785	0.67	47	21	26	1722	54	7	52	0.563
92-23	460	470	15843	0.4	1	0.1	7192	0.25	43	33	31	1257	65	7	60	0.753
92-23	470	480	15844	0.3	1	0.1	5125	0.58	19	24	24	2085	46	7	46	0.564
92-23	480	490	15845	1.1	1	0.1	10000	0.37	99	50	24	1722	58	6	84	1.120
92-23	490	500	15846	2.3	1	0.1	8675	0.27	10	40	22	2042	58	7	87	0.910
92-23	500	510	15847	2.9	1	0.1	7726	0.07	16	35	21	705	45	7	82	0.854
92-23	510	520	15848	1.9	2	0.1	5789	0.13	18	22	21	1105	40	5	65	0.631
92-23	520	530	15849	0.4	1	0.1	3143	0.19	19	14	17	1386	38	6	49	0.337
92-23	530	540	15850	1.0	1	0.1	5212	0.40	34	24	17	2201	46	7	70	0.545
92-23	540	550	15100	0.1	1	0.1	4250	0.25	29	13	18	1326	47	6	60	0.451

II - 172

I.C.P., Au - fire geochem and Cu-assay

New Canamin Resources Huckleberry

Min-En Laboratories
705 West 15th St.
North Vancouver, B.C.
Tel. (604) 980-5814

HOLE#	INTERVAL(feet)	SAMPL	AG	AS	CD	CU	K	MO	NI	PB	TI	ZN	W	AU	CU-ASSAY	
HOLE#	START	END	SAMPL	PPM	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPB	%	
92-24B	75	80	15851	0.4	1	0.1	2912	1.09	5	1	21	2549	34	5	33	0.309
92-24B	80	90	15852	0.5	1	0.1	4084	0.77	34	1	19	1985	37	5	34	0.447
92-24B	90	100	15853	4.6	1	0.1	4842	1.23	22	1	18	2420	32	7	58	0.526
92-24B	100	110	15854	0.5	1	0.1	4437	0.86	21	1	18	2114	34	6	26	0.440
92-24B	110	120	15855	0.1	1	0.1	3763	1.17	7	1	17	2905	35	7	23	0.386
92-24B	120	130	15856	1.5	1	0.1	6512	0.43	58	3	19	1477	35	5	47	0.639
92-24B	130	140	15857	0.6	1	0.1	4035	0.67	43	1	20	1917	33	6	43	0.440
92-24B	140	150	15858	0.7	1	0.1	1744	0.55	53	1	19	1314	33	5	18	0.190
92-24B	150	160	15859	1.6	1	0.1	1575	0.34	114	2	18	546	30	5	17	0.157
92-24B	160	170	15860	1.2	4	0.1	2753	0.26	82	6	17	339	26	4	29	0.291
92-24B	170	180	15861	0.1	1	0.1	4092	1.68	80	21	19	2163	48	9	33	0.414
92-24B	180	190	15862	0.9	6	0.1	1682	0.27	100	2	13	342	24	5	26	0.174
92-24B	190	200	15863	0.6	2	0.1	1260	0.30	177	1	12	211	19	5	18	0.132
92-24B	200	210	15864	0.5	11	0.1	1942	0.33	149	4	16	403	29	5	22	0.208
92-24B	210	220	15865	0.1	1	0.1	1314	0.36	104	1	14	1116	22	4	20	0.140
92-24B	220	230	15866	0.1	1	0.1	2597	1.06	124	1	20	2181	36	7	29	0.253
92-24B	230	240	15867	0.3	1	0.1	4144	1.02	52	1	20	2958	37	6	57	0.412
92-24B	240	250	15868	1.0	1	0.1	3605	0.62	110	2	18	2114	32	7	26	0.347
92-24B	250	260	15869	0.1	1	0.1	1973	0.65	70	1	19	1841	33	5	18	0.198
92-24B	260	270	15870	1.1	1	0.1	3733	0.58	215	1	21	1733	36	6	38	0.379
92-24B	270	280	15871	0.5	1	0.1	3754	0.88	169	1	17	1743	34	5	79	0.373
92-24B	280	290	15872	0.9	1	0.1	2687	0.38	145	1	16	1489	26	6	29	0.274
92-24B	290	300	15873	0.2	1	0.1	2103	0.38	211	1	14	1418	25	6	34	0.214
92-24B	300	310	15874	1.5	1	0.1	4252	0.26	340	1	17	1360	31	6	36	0.441
92-24B	310	320	15875	1.6	1	0.1	4560	0.58	113	1	12	2160	34	6	49	0.511
92-24B	320	330	15876	2.2	1	0.1	6599	0.49	131	1	17	2586	43	7	78	0.695
92-24B	330	340	15877	1.5	1	0.1	6093	0.84	175	1	19	3046	47	7	58	0.634
92-24B	340	350	15878	1.8	1	0.1	4875	0.22	266	4	22	883	49	7	36	0.548
92-24B	350	360	15879	1.4	7	0.1	3909	0.20	1619	7	17	442	50	7	82	0.435
92-24B	360	370	15880	1.2	1	0.1	3540	0.20	1005	10	25	1131	51	9	42	0.372
92-24B	370	380	15881	1.1	1	0.1	2991	0.28	24	8	15	1646	46	8	50	0.325
92-24B	380	390	15882	0.7	1	0.1	2292	0.23	72	8	17	1636	45	9	34	0.245
92-24B	390	400	15883	0.6	1	0.1	1758	0.24	71	5	12	1869	46	7	20	0.197
92-24B	400	410	15884	1.3	1	0.1	3141	0.32	52	4	14	1794	39	7	46	0.325
92-24B	410	420	15885	2.5	1	0.1	2748	0.32	83	6	16	1789	37	7	36	0.299
92-24B	420	430	15886	1.3	1	0.1	2835	0.28	28	7	15	1769	40	8	39	0.307

II - 173

I.C.P., Au - fire geochem and Cu-assay

New Canamin Resources

Huckleberry

Min-En Laboratories
705 West 15th St.
North Vancouver, B.C.
Tel. (604) 980-5814

HOLE#	INTERVAL(feet)	SAMPL	AG	AS	CD	CU	K	MO	NI	PB	TI	ZN	W	AU	CU-ASSAY	
HOLE#	START	END	SAMPL	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPB	%	
92-24B	430	440	15887	1.4	1	0.1	3100	0.22	227	7	20	1368	40	8	35	0.341
92-24B	440	450	15888	0.6	1	0.1	1938	0.18	63	5	14	1304	39	7	25	0.212
92-24B	450	460	15889	1.5	1	0.1	3466	0.24	106	7	18	1639	43	10	45	0.359
92-24B	460	470	15890	1.1	1	0.1	2694	0.19	42	4	12	1638	36	7	44	0.308
92-24B	470	480	15891	0.7	1	0.1	2084	0.11	20	5	17	1526	41	7	55	0.229
92-24B	480	490	15892	0.1	1	0.1	1685	0.15	76	3	17	1359	40	8	38	0.179
92-24B	490	500	15893	0.1	1	0.1	3880	0.47	75	4	15	2516	46	8	71	0.415
92-24B	500	510	15894	0.1	1	0.1	5158	0.65	52	2	18	2993	52	9	63	0.540
92-24B	510	520	15895	0.4	1	0.1	4331	0.50	24	4	17	2513	49	8	49	0.447
92-24B	520	530	15896	4.1	1	0.1	10000	0.34	112	5	27	2906	63	12	119	1.120
92-24B	530	540	15897	0.9	1	0.1	3676	0.23	13	1	14	3134	43	8	45	0.371
92-24B	540	550	15898	0.6	1	0.1	5013	0.26	82	2	15	3150	48	8	52	0.525
92-24B	550	560	15899	0.1	1	0.1	4499	0.27	104	1	22	2274	47	7	43	0.479
92-24B	560	570	15900	0.8	1	0.1	2385	0.25	68	1	15	1539	37	6	27	0.255
92-24B	580	590	15094	0.7	1	0.1	3021	0.35	564	1	21	1493	39	5	27	0.345
92-24B	590	600	15095	0.5	1	0.1	7189	0.35	57	1	19	1605	49	7	64	0.743
92-24B	600	610	15096	0.1	1	0.1	4238	0.90	58	1	15	2901	49	7	19	0.449
92-24B	610	620	15097	0.1	1	0.1	2988	0.74	25	1	18	2707	51	8	29	0.336
92-24B	620	630	15098	0.1	1	0.1	2309	0.97	26	1	9	3301	46	7	19	0.262
92-24B	630	640	15099	0.1	1	0.1	4742	0.90	68	1	18	2834	48	6	50	0.582

AL-11

I.C.P., Au - fire geochem and Cu-assay

New Canamin Resources

Huckleberry

Min-En Laboratories
705 West 15th St.
North Vancouver, B.C.
Tel. (604) 980-5814

51-175

HOLE#	INTERVAL(feet)	SAMPL	AG	AS	CD	CU	K	MO	NI	PB	TI	ZN	W	AU	CU-ASSAY	
HOLE#	START	END	SAMPL	PPM	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPB	%	
92-25	40	50	15901	0.6	1	0.1	2802	0.96	28	1	10	2375	39	6	27	0.280
92-25	50	60	15902	1.1	1	0.1	3676	0.77	42	1	11	2730	40	6	30	0.387
92-25	85	90	15903	1.5	1	0.1	5208	0.58	76	6	14	2292	41	7	53	0.558
92-25	90	100	15904	2.5	1	0.1	7022	0.72	79	4	16	2599	49	7	62	0.748
92-25	100	110	15905	1.3	1	0.1	5843	0.86	70	5	15	2786	39	7	104	0.606
92-25	110	120	15906	0.7	1	0.1	3545	0.57	111	2	17	2215	34	7	47	0.380
92-25	120	130	15907	2.0	1	0.1	4229	0.50	129	7	17	1469	37	7	42	0.441
92-25	130	140	15908	1.4	1	0.1	3043	0.26	218	5	15	420	32	7	37	0.313
92-25	140	150	15909	1.0	1	0.1	3019	0.33	55	7	11	589	32	6	34	0.315
92-25	150	160	15910	1.0	1	0.1	2331	0.37	79	3	13	335	29	5	33	0.232
92-25	160	170	15911	1.3	1	0.1	2509	0.29	111	9	15	199	28	6	27	0.260
92-25	170	180	15912	1.1	1	0.1	2928	0.29	173	5	12	686	30	6	36	0.323
92-25	180	190	15913	0.9	1	0.1	4041	0.60	88	7	12	2077	43	7	44	0.427
92-25	190	200	15914	0.1	1	0.1	3850	1.01	54	1	18	3097	46	8	48	0.401
92-25	200	210	15915	1.2	1	0.1	3882	0.72	149	2	16	2243	35	8	45	0.390
92-25	210	220	15916	1.1	1	0.1	3611	0.39	76	6	15	2331	39	7	43	0.356
92-25	220	230	15917	0.9	1	0.1	3316	0.38	91	3	14	1884	31	6	33	0.363
92-25	230	240	15918	2.4	1	0.1	9254	0.50	136	17	20	2534	56	8	95	0.980
92-25	240	250	15919	1.6	1	0.1	6290	0.92	122	9	25	2931	73	9	79	0.667
92-25	250	260	15920	1.4	1	0.1	4939	0.66	103	8	35	2857	114	8	54	0.563
92-25	260	270	15921	3.7	1	0.1	8304	0.37	492	12	19	2476	49	8	111	0.830
92-25	270	280	15922	3.8	1	0.1	7084	0.47	201	4	17	2837	41	8	57	0.731
92-25	280	290	15923	2.5	1	0.1	5703	0.28	721	4	20	2742	41	7	93	0.599
92-25	290	300	15924	3.5	1	0.1	6703	0.40	137	1	19	2959	50	8	65	0.679
92-25	300	310	15925	1.1	1	0.1	5801	0.41	156	7	18	2226	47	7	96	0.588
92-25	310	320	15926	0.1	1	0.1	2126	0.34	176	4	12	2057	46	7	38	0.219
92-25	320	330	15927	0.8	1	0.1	2421	0.23	95	10	16	1996	46	7	29	0.249
92-25	330	340	15928	3.9	1	0.1	3549	0.25	30	9	13	1815	48	8	49	0.367
92-25	340	350	15929	1.5	1	0.1	4574	0.22	212	11	23	1739	45	7	44	0.469
92-25	350	360	15930	0.7	1	0.1	3527	0.15	87	7	33	1401	91	6	40	0.371
92-25	360	370	15931	1.1	1	0.1	3273	0.14	110	9	27	1348	56	7	39	0.356
92-25	370	380	15932	1.2	1	0.1	3049	0.16	133	9	48	1543	112	7	30	0.331
92-25	380	390	15933	0.3	1	0.1	1852	0.17	192	10	14	1639	48	7	22	0.198
92-25	390	400	15934	0.3	1	0.1	2557	0.15	282	7	14	1328	49	7	33	0.264
92-25	400	410	15935	0.2	1	0.1	2340	0.13	60	11	21	1590	61	7	24	0.229
92-25	410	420	15936	0.3	1	0.1	2211	0.16	177	8	18	1653	55	7	38	0.224

I.C.P., Au - fire geochem and Cu-assay

New Canamin Resources

Huckleberry

Min-En Laboratories
705 West 15th St.
North Vancouver, B.C.
Tel. (604) 980-5814

HOLE#	INTERVAL(feet)	SAMPL	AG	AS	CD	CU	K	MO	NI	PB	TI	ZN	W	AU	CU-ASSAY	
HOLE#	START	END	SAMPL	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPB	%	
92-25	420	430	15937	0.1	1	0.1	1708	0.16	74	11	14	1252	56	7	32	0.175
92-25	430	440	15938	0.2	1	0.1	2485	0.22	65	10	14	1462	88	8	23	0.238
92-25	440	450	15939	0.1	1	0.1	1152	0.14	218	10	19	1016	59	7	15	0.120
92-25	450	460	15940	0.3	1	0.1	2580	0.20	280	9	18	830	53	7	50	0.276
92-25	460	470	15941	0.1	1	0.1	1798	0.14	70	9	19	1125	54	7	9	0.188
92-25	470	480	15942	1.5	1	0.1	3394	0.23	108	10	19	1270	53	8	33	0.349
92-25	480	490	15943	0.5	1	0.1	2203	0.14	30	10	19	1681	53	8	15	0.230
92-25	490	500	15944	0.3	1	0.1	2278	0.11	123	9	19	1440	55	7	37	0.239

DL-17C

New Canamin Resources

Huckleberry

Min-En Laboratories
705 West 15th St.
North Vancouver, B.C.
Tel. (604) 980-5814

HOLE#	INTERVAL(feet)	SAMPL	AG	AS	CD	CU	K	MO	NI	PB	TI	ZN	W	AU	CU-ASSAY	
HOLE#	START	END	SAMPL	PPM	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPB	%	
92-26	50	60	15951	0.1	1	0.1	5156	0.69	462	8	16	2208	50	7	48	0.526
92-26	60	70	15952	0.3	1	0.1	5116	0.64	65	4	14	2301	43	7	49	0.539
92-26	70	80	15953	1.2	1	0.1	3950	0.39	46	4	12	1425	38	6	39	0.411
92-26	80	90	15954	2.0	1	0.1	6821	0.45	38	4	18	1986	43	7	76	0.740
92-26	90	100	15955	3.9	1	0.1	10000	0.30	97	6	23	1127	45	8	95	1.030
92-26	100	110	15956	5.2	1	0.1	10000	0.38	45	7	27	1679	59	8	127	1.178
92-26	110	120	15957	3.5	1	0.1	10000	0.41	79	8	27	1614	64	8	112	1.590
92-26	120	130	15958	1.7	1	0.1	10000	0.42	66	6	23	1780	55	9	121	1.130
92-26	130	140	15959	2.6	1	0.1	10000	0.48	18	4	25	1900	62	11	180	1.450
92-26	140	150	15960	4.3	1	0.1	10000	0.58	185	11	25	2235	55	10	182	1.540
92-26	150	160	15961	2.9	1	0.1	10000	0.43	66	3	19	2338	46	9	102	1.090
92-26	160	170	15962	1.4	1	0.1	6357	0.51	96	4	17	2144	41	11	98	0.717
92-26	170	180	15963	1.9	1	0.1	7031	0.54	176	4	16	1978	41	8	126	0.770
92-26	180	190	15964	1.9	1	0.1	7155	0.37	69	4	23	1931	44	8	111	0.755
92-26	190	200	15965	3.8	1	0.1	9911	0.37	77	4	24	1037	153	7	109	1.050
92-26	200	210	15966	2.4	1	0.1	5602	0.16	60	5	15	919	32	6	65	0.629
92-26	210	220	15967	5.6	1	0.1	9281	0.21	244	9	25	1077	51	7	77	0.980
92-26	220	230	15968	7.7	23	0.1	10000	0.25	8726	11	40	1199	62	10	278	2.150
92-26	230	240	15969	9.8	1	0.1	10000	0.46	2697	4	41	1862	196	9	170	1.680
92-26	240	250	15970	2.8	1	0.1	9169	0.34	161	3	19	1330	41	8	106	0.950
92-26	250	260	15971	1.4	1	0.1	6081	0.56	125	1	17	2037	47	7	99	0.653
92-26	260	270	15972	1.4	1	0.1	5217	0.46	84	2	18	1497	42	7	64	0.540
92-26	270	280	15973	2.5	1	0.1	10000	0.21	124	6	27	1189	47	8	223	1.110
92-26	280	290	15974	3.1	1	0.1	10000	0.54	46	12	29	1611	61	9	204	1.450
92-26	290	300	15975	0.9	1	0.1	7011	0.59	180	6	23	1458	49	7	102	0.766
92-26	300	310	15976	0.9	1	0.1	8477	0.62	75	1	24	1769	70	7	82	0.850
92-26	310	320	15977	2.2	1	0.1	9257	0.26	127	7	22	1333	60	6	154	1.000
92-26	320	330	15978	1.7	1	0.1	7146	0.26	192	6	28	1484	62	7	80	0.816
92-26	330	340	15979	1.9	1	0.1	7169	0.19	758	6	21	1575	63	6	92	0.751
92-26	340	350	15980	8.1	1	0.1	10000	0.14	50	6	26	1688	78	8	136	1.590
92-26	350	360	15981	2.1	1	0.1	9210	0.51	36	6	18	2361	57	7	104	0.970
92-26	360	370	15982	1.8	1	0.1	7331	0.19	49	9	20	1380	56	7	75	0.735
92-26	370	380	15983	1.5	1	0.1	3935	0.13	97	13	17	1400	59	7	48	0.435
92-26	380	390	15984	0.7	1	0.1	3542	0.08	66	12	15	1333	42	8	70	0.400
92-26	390	400	15985	0.8	1	0.1	3606	0.07	60	8	14	1012	50	6	39	0.394
92-26	400	410	15986	0.1	1	0.1	3101	0.08	20	7	14	1378	39	8	25	0.327

II-177

I.C.P., Au - fire geochem and Cu-assay

New Canamin Resources

Huckleberry

Min-En Laboratories
705 West 15th St.
North Vancouver, B.C.
Tel. (604) 980-5814

HOLE#	INTERVAL(feet)	SAMPL	AG	AS	CD	CU	K	MO	NI	PB	TI	ZN	W	AU	CU-ASSAY	
HOLE#	START	END	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPB	%	
92-26	410	420	15986	0.4	1	0.1	2763	0.06	27	4	14	1301	45	7	25	0.435
92-26	420	430	15987	0.5	1	0.1	3974	0.06	47	3	15	1271	48	7	36	0.290
92-26	430	440	15989	0.7	1	0.1	3164	0.08	48	6	16	1345	43	9	27	0.337
92-26	440	450	15990	0.4	1	0.1	2246	0.14	35	7	10	1267	36	7	19	0.235
92-26	450	460	15991	0.4	10	0.1	1040	0.16	103	5	11	479	24	6	5	0.118

861-11

I.C.P., Au - fire geochem and Cu-assay

New Canamin Resources Huckleberry

Min-En Laboratories
705 West 15th St.
North Vancouver, B.C.
Tel. (604) 980-5814

HOLE#	INTERVAL(feet)		SAMPL	AG	AS	CD	CU	K	MO	NI	PB	TI	ZN	W	AU	CU-ASSAY
HOLE#	START	END	SAMPL	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPB	%
92-27	60	70	17001	0.1	1	0.1	2447	0.49	90	2	15	1156	38	7	35	0.290
92-27	70	80	17002	0.6	1	0.1	3192	0.56	50	2	12	1130	34	5	40	0.385
92-27	80	90	17003	0.5	1	0.1	3813	0.13	68	5	19	717	34	5	64	0.453
92-27	90	100	17004	0.5	1	0.1	4807	0.18	92	16	20	524	41	7	103	0.613
92-27	100	110	17005	0.1	1	0.1	3646	0.11	102	20	19	444	39	5	65	0.480
92-27	110	120	17006	0.1	1	0.1	2127	0.11	34	35	22	405	38	5	66	0.262
92-27	120	130	17007	0.1	1	0.1	3762	0.26	76	3	15	742	36	5	64	0.447
92-27	130	140	17008	0.6	1	0.1	4822	0.28	29	8	16	710	50	6	759	0.599
92-27	140	150	17009	0.1	1	0.1	2056	0.21	32	82	17	1200	53	6	32	0.225
92-27	150	160	17010	0.6	1	0.1	4963	0.17	108	8	15	921	43	6	59	0.609
92-27	160	170	17011	0.7	1	0.1	4853	0.29	135	10	13	1305	40	6	47	0.574
92-27	170	180	17012	0.1	1	0.1	3067	0.37	86	4	8	1680	37	8	31	0.356
92-27	180	190	17013	0.4	1	0.1	4124	0.27	40	7	14	1372	40	6	68	0.466
92-27	190	200	17014	0.3	1	0.1	3666	0.24	32	5	11	1449	39	8	30	0.428
92-27	200	210	17015	0.1	1	0.1	3823	0.26	40	5	12	1457	40	10	31	0.446
92-27	210	220	17016	0.1	1	0.1	3364	0.30	174	4	13	1650	48	8	19	0.364
92-27	220	230	17017	0.7	1	0.1	4146	0.31	138	6	19	1630	48	9	32	0.470
92-27	230	240	17018	1.3	1	0.1	4720	0.22	39	8	14	1558	45	8	92	0.554
92-27	240	250	17019	0.1	1	0.1	4826	0.35	106	7	17	2053	50	10	39	0.526
92-27	250	260	17020	0.1	1	0.1	4261	0.46	52	7	15	1885	42	8	26	0.475
92-27	260	270	17021	0.1	1	0.1	2451	0.16	10	5	12	1701	33	6	27	0.272
92-27	270	280	17022	0.1	1	0.1	2865	0.18	58	6	12	1174	32	6	31	0.318
92-27	280	290	17023	0.1	1	0.1	3246	0.17	136	9	13	983	35	5	47	0.380
92-27	290	300	17024	0.3	1	0.1	3424	0.24	52	12	17	1056	33	5	61	0.396
92-27	300	310	17025	1.3	1	0.1	4471	0.13	168	18	13	2173	39	6	73	0.479

671-179

I.C.P., Au - fire geochem and Cu-assay

New Canamin Resources Huckleberry

Min-En Laboratories
705 West 15th St.
North Vancouver, B.C.
Tel. (604) 980-5814

HOLE#	INTERVAL(feet)	SAMPL	AG	AS	CD	CU	K	MO	NI	PB	TI	ZN	W	AU	CU-ASSAY	
HOLE#	START	END	SAMPL	PPM	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPB	%	
92-28	20	30	17051	0.1	1	0.1	2199	0.39	35	8	19	2079	45	8	35	0.241
92-28	30	40	17052	0.1	1	0.1	3277	0.46	24	3	16	2158	44	9	57	0.354
92-28	40	50	17053	0.1	1	0.1	1241	0.77	8	1	19	2681	50	8	22	0.129
92-28	50	60	17054	0.1	1	0.1	1978	0.46	12	1	18	1841	51	8	27	0.218
92-28	60	70	17055	1.0	1	0.1	4812	0.20	22	2	17	1750	48	7	73	0.514
92-28	70	80	17056	0.6	1	0.1	4221	0.28	18	1	16	1711	49	7	58	0.427
92-28	80	90	17057	0.5	1	0.1	3936	0.18	9	1	15	2188	40	10	54	0.405
92-28	90	100	17058	0.6	1	0.1	3825	0.23	36	3	15	935	34	7	52	0.398
92-28	100	110	17059	0.4	5	0.1	3049	0.35	58	5	20	310	52	9	37	0.306
92-28	110	120	17060	0.2	4	0.1	2986	0.31	69	6	13	181	43	6	43	0.336
92-28	120	130	17061	0.1	1	0.1	2632	0.13	54	4	16	1329	28	6	38	0.284
92-28	130	140	17062	1.1	1	0.1	7647	0.12	238	16	21	2112	46	8	82	0.783
92-28	140	150	17063	1.1	1	0.1	8773	0.12	133	25	22	1815	49	8	58	0.890
92-28	150	160	17064	1.1	1	0.1	9225	0.35	84	47	21	2599	57	9	95	0.910
92-28	160	170	17065	1.3	1	0.1	8301	0.12	88	34	22	1984	51	8	71	0.860
92-28	170	180	17066	1.6	1	0.1	8185	0.15	49	34	19	2027	46	8	55	0.850
92-28	180	190	17067	0.7	1	0.1	4951	0.13	83	22	17	1860	31	7	37	0.517
92-28	190	200	17068	0.3	1	0.1	3294	0.23	73	11	17	1811	30	6	42	0.333
92-28	200	210	17069	0.7	1	0.1	4788	0.21	98	4	19	1363	35	6	39	0.500
92-28	210	220	17070	0.5	1	0.1	4498	0.16	77	1	19	1242	33	6	42	0.476
92-28	220	230	17071	0.1	1	0.1	3420	0.23	107	1	17	1699	28	7	38	0.374
92-28	230	240	17072	0.1	1	0.1	2988	0.27	196	1	14	1995	28	7	25	0.298
92-28	240	250	17073	0.1	1	0.1	2717	0.27	138	2	17	793	21	6	32	0.292
92-28	250	260	17074	0.1	1	0.1	1876	0.23	43	1	16	1449	24	6	16	0.192
92-28	260	270	17075	0.7	1	0.1	3189	0.30	83	1	16	1791	27	8	29	0.335
92-28	270	280	17076	0.7	1	0.1	3466	0.41	45	1	12	3512	29	7	28	0.270
92-28	280	290	17077	0.1	1	0.1	2725	0.41	70	1	13	2844	23	7	31	0.290
92-28	290	300	17078	0.1	1	0.1	2119	0.29	125	1	15	1166	27	6	17	0.227
92-28	300	310	17079	0.1	1	0.1	1651	0.34	67	1	13	1404	24	6	12	0.179
92-28	310	320	17080	0.1	1	0.1	3419	0.52	114	1	18	1271	34	6	28	0.371
92-28	320	330	17081	0.1	1	0.1	3103	0.68	40	1	14	2580	35	9	27	0.341
92-28	330	340	17082	0.1	1	0.1	3458	0.70	40	1	13	3351	39	8	71	0.392
92-28	340	350	17083	0.1	1	0.1	3483	0.40	56	1	11	2242	31	7	29	0.387
92-28	350	360	17084	0.2	1	0.1	3335	0.24	67	1	19	1333	34	8	26	0.356
92-28	360	370	17085	1.0	1	0.1	4699	0.18	73	3	14	1200	34	8	33	0.540
92-28	370	380	17086	0.5	1	0.1	6375	0.23	136	3	21	1076	40	7	64	0.723

031-II

I.C.P., Au - fire geochem and Cu-assay

New Canamin Resources Huckleberry

Min-En Laboratories
705 West 15th St.
North Vancouver, B.C.
Tel. (604) 980-5814

HOLE#	INTERVAL(feet)	SAMPL	AG	AS	CD	CU	K	MO	NI	PB	TI	ZN	W	AU	CU-ASSAY	
HOLE#	START	END	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPB	%	
92-28	380	390	17087	0.4	1	0.1	5133	0.35	48	1	17	2141	38	8	35	0.582
92-28	390	400	17088	0.1	1	0.1	6488	0.61	65	6	27	1681	49	11	38	0.715
92-28	400	410	17089	0.1	1	0.1	6343	0.69	112	1	21	2983	47	10	44	0.718
92-28	410	420	17090	0.1	1	0.1	5357	1.01	287	1	19	3839	47	10	26	0.577
92-28	420	430	17091	0.1	1	0.1	6229	0.68	103	1	20	3280	49	13	32	0.657
92-28	430	440	17092	0.1	1	0.1	6356	0.52	366	1	22	2688	53	12	44	0.629
92-28	440	450	17093	0.9	1	0.1	9262	0.39	73	1	27	1965	63	19	71	0.980
92-28	450	460	17094	0.1	1	0.1	5027	0.46	48	1	17	1926	43	8	41	0.557
92-28	460	470	17095	0.1	1	0.1	3923	0.47	88	1	15	2458	40	9	52	0.461
92-28	470	480	17096	0.1	1	0.1	4775	0.35	249	1	17	2829	41	12	40	0.533
92-28	480	490	17097	0.1	1	0.1	3468	0.57	66	1	15	3170	43	9	21	0.391
92-28	490	500	17098	0.1	1	0.1	3858	0.72	25	1	13	2592	44	8	43	0.438
92-28	500	510	17099	0.1	1	0.1	3369	0.41	42	1	15	1551	36	7	31	0.378
92-28	510	520	17100	0.1	1	0.1	3033	0.41	23	1	16	1549	52	7	28	0.363
92-28	520	530	15091	0.1	7	0.1	1815	0.71	15	1	19	1332	66	6	10	0.194
92-28	530	540	15092	0.1	1	0.1	3273	0.18	65	5	13	741	33	7	26	0.354
92-28	540	550	15093	0.7	1	0.1	4221	0.39	158	2	16	2126	35	8	28	0.421

181-II

New Canamin Resources

Huckleberry

23/12

HOLE#	INTERVAL(feet)	SAMPL	AG	AS	CD	CU	K	MO	NI	PB	TI	ZN	W	AU	CU-ASSAY	
HOLE#	START	END	SAMPL	PPM	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPB	%	
92-29	10	20	17101	0.4	1	0.1	2838	0.69	202	4	19	2804	33	7	27	0.301
92-29	20	30	17102	0.1	1	0.1	1421	0.42	46	2	14	1432	28	6	15	0.176
92-29	30	40	17103	0.1	1	0.1	764	0.23	47	4	12	379	24	6	12	0.084
92-29	40	50	17104	0.1	1	0.1	1486	0.27	58	4	13	1355	26	7	21	0.071
92-29	50	60	17105	0.1	1	0.1	1444	0.41	204	2	16	1641	30	6	18	0.163
92-29	60	70	17106	0.1	1	0.1	2007	0.32	77	2	16	1123	29	6	21	0.230
92-29	70	80	17107	2.2	1	0.1	9248	0.50	370	5	23	1487	39	8	75	0.990
92-29	80	90	17108	0.1	1	0.1	2600	0.86	109	12	20	1792	36	8	30	0.293
92-29	90	100	17109	0.1	1	0.1	3787	0.49	101	12	20	1884	35	8	40	0.418
92-29	100	110	17110	0.7	1	0.1	4998	0.29	123	9	24	1343	37	9	70	0.509
92-29	110	120	17111	0.3	1	0.1	4440	0.31	127	5	23	1287	38	8	38	0.453
92-29	120	130	17112	0.3	1	0.1	3249	0.27	129	4	20	1271	33	8	30	0.350
92-29	130	140	17113	0.1	1	0.1	3815	0.28	80	5	20	1516	33	8	39	0.400
92-29	140	150	17114	0.3	1	0.1	3445	0.40	119	2	22	1017	32	8	37	0.370
92-29	150	160	17115	0.1	1	0.1	2361	0.32	133	2	19	960	28	10	30	0.247
92-29	160	170	17116	0.1	1	0.1	2590	0.28	105	2	19	1455	30	7	28	0.291
92-29	170	180	17117	0.1	1	0.1	2315	0.36	170	1	17	1330	32	7	27	0.242
92-29	180	190	17118	0.5	1	0.1	3710	0.30	81	1	23	1143	33	7	44	0.382
92-29	190	200	17119	0.6	1	0.1	3389	0.42	391	1	21	1199	36	9	27	0.346
92-29	200	210	17120	1.3	1	0.1	5128	0.35	121	2	22	718	41	8	44	0.514
92-29	210	220	17121	1.0	1	0.1	3229	0.31	46	2	23	1807	37	9	31	0.332
92-29	220	230	17122	0.1	1	0.1	1959	0.30	20	1	16	1290	26	7	14	0.198
92-29	230	240	17123	0.3	1	0.1	1993	0.50	72	1	19	1371	27	7	37	0.212
92-29	240	250	17124	0.2	1	0.1	4062	0.50	165	1	18	1968	33	7	46	0.422
92-29	250	260	17125	0.1	1	0.1	2768	0.43	123	1	15	2528	31	7	36	0.291
92-29	260	270	17126	0.1	1	0.1	3495	0.42	97	1	14	1833	28	6	36	0.372
92-29	270	280	17127	0.1	1	0.1	2520	0.36	84	1	9	1451	25	6	24	0.249
92-29	280	290	17128	0.1	1	0.1	2228	0.38	117	1	13	1500	27	7	24	0.232
92-29	290	300	17129	0.1	1	0.1	2637	0.36	191	1	13	1677	28	6	23	0.271
92-29	300	310	17130	0.1	1	0.1	3756	0.48	38	1	12	2976	34	9	38	0.380
92-29	310	320	17131	0.1	1	0.1	4442	0.80	70	1	19	3091	43	10	35	0.412
92-29	320	330	17132	0.1	1	0.1	5043	0.83	65	1	14	2437	42	8	44	0.471
92-29	330	340	17133	0.1	1	0.1	5122	0.93	143	1	19	2451	44	9	57	0.533
92-29	340	350	17134	0.1	1	0.1	4126	0.96	62	1	22	2511	43	9	41	0.439
92-29	350	360	17135	0.7	1	0.1	3203	0.53	45	1	16	3093	34	8	37	0.331
92-29	360	370	17136	0.2	1	0.1	2533	0.84	12	1	14	2979	32	9	23	0.275

I.C.P., Au - fire geochem and Cu-assay

New Canamin Resources

Huckleberry

Min-En Laboratories
705 West 15th St.
North Vancouver, B.C.
Tel. (604) 980-5814

HOLE#	INTERVAL(feet)	SAMPL	AG	AS	CD	CU	K	MO	NI	PB	TI	ZN	W	AU	CU-ASSAY	
HOLE#	START	END	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPB	%	
92-29	370	380	17137	0.1	1	0.1	2939	0.94	121	1	16	2898	40	10	29	0.308
92-29	380	390	17138	0.1	1	0.1	3776	0.83	72	1	18	3261	45	12	41	0.387
92-29	390	400	17139	0.1	1	0.1	3304	0.64	73	1	14	3158	50	11	45	0.338
92-29	400	410	17140	0.1	1	0.1	6066	0.65	59	1	17	3177	53	11	52	0.630
92-29	410	417	17141	0.1	1	0.1	9694	0.81	126	5	27	3260	65	11	118	1.050

II-103

I.C.P., Au - fire geochem and Cu-assay

New Canamin Resources Huckleberry

Min-En Laboratories
705 West 15th St.
North Vancouver, B.C.
Tel. (604) 980-5814

HOLE#	INTERVAL(feet)		SAMPL	AG	AS	CD	CU	K	MO	NI	PB	TI	ZN	W	AU	CU-ASSAY
HOLE#	START	END	SAMPL	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPB	%
92-31	10	20	17151	0.1	1	0.1	1359	0.38	47	2	9	1868	23	6	19	0.137
92-31	20	30	17152	0.1	1	0.1	1475	0.53	72	1	12	1655	25	6	13	0.154
92-31	30	40	17153	0.1	1	0.1	1501	0.46	67	1	14	1795	21	7	17	0.159
92-31	40	50	17154	0.1	1	0.1	3244	0.48	68	1	14	1575	28	6	30	0.350
92-31	50	60	17155	0.1	1	0.1	1715	0.43	75	1	13	2044	22	6	18	0.181
92-31	60	70	17156	0.1	1	0.1	1535	0.36	21	1	18	2099	29	8	14	0.162
92-31	70	80	17157	0.1	1	0.1	1263	0.59	24	5	24	2425	30	11	16	0.146
92-31	80	90	17158	0.6	2	0.1	2418	0.35	40	3	25	1488	33	9	27	0.277
92-31	90	100	17159	0.1	1	0.1	2169	0.28	51	1	17	1777	32	7	30	0.251
92-31	100	110	17160	0.1	1	0.1	2351	0.24	45	3	17	1510	31	8	26	0.259
92-31	110	120	17161	0.1	1	0.1	1339	0.27	35	1	18	1600	27	7	18	0.150
92-31	120	130	17162	0.1	1	0.1	1355	0.34	88	1	22	1251	39	7	14	0.144
92-31	130	140	17163	0.1	1	0.1	1497	0.31	47	1	14	653	24	6	16	0.166
92-31	140	150	17164	0.1	1	0.1	1447	0.54	23	1	19	2093	33	8	17	0.150
92-31	150	160	17165	0.1	1	0.1	2030	0.43	58	1	14	1419	26	5	24	0.227
92-31	160	170	17166	0.1	1	0.1	1661	0.27	96	1	13	1012	22	5	20	0.185
92-31	170	180	17167	0.1	1	0.1	2453	0.86	79	2	20	1921	31	6	27	0.259
92-31	180	190	17168	0.1	1	0.1	2500	0.33	76	2	15	1309	27	6	29	0.277
92-31	190	200	17169	0.1	1	0.1	3365	0.89	236	9	29	2050	42	8	36	0.376
92-31	200	210	17170	0.1	1	0.1	2294	2.09	71	17	20	3801	49	11	23	0.247
92-31	210	220	17171	0.1	1	0.1	2914	1.22	85	18	22	2117	35	9	36	0.323
92-31	220	230	17172	0.1	1	0.1	3461	0.83	207	6	17	2330	34	8	50	0.386
92-31	230	240	17173	0.1	1	0.1	3428	0.28	111	1	13	2143	29	6	28	0.369
92-31	240	250	17174	0.1	1	0.1	3426	0.55	43	1	13	2722	36	9	32	0.375
92-31	250	260	17175	0.1	1	0.1	2418	1.03	43	1	22	3564	41	9	28	0.266
92-31	260	270	17176	0.1	1	0.1	2061	0.45	86	1	18	1790	28	7	20	0.232
92-31	270	280	17177	0.1	1	0.1	2073	0.51	103	1	16	2602	34	8	19	0.224
92-31	280	290	17178	0.3	1	0.1	4501	0.56	77	1	20	1558	52	7	44	0.500
92-31	290	300	17179	0.1	1	0.1	4287	0.70	53	1	17	1615	38	7	38	0.440

431-11

I.C.P., Au - fire geochem and Cu-assay

New Canamin Resources

Huckleberry

Min-En Laboratories
705 West 15th St.
North Vancouver, B.C.
Tel. (604) 980-5814

HOLE#	INTERVAL(feet)	SAMPL	AG	AS	CD	CU	K	MO	NI	PB	TI	ZN	W	AU	CU-ASSAY	
HOLE#	START	END	SAMPL	PPM	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPB	%	
92-32	50	60	17201	0.1	1	0.1	9328	0.85	7	1	20	2678	50	9	103	1.070
92-32	60	70	17202	0.1	1	0.1	2796	0.23	426	5	20	863	37	7	34	0.311
92-32	70	80	17203	0.2	1	0.1	3266	0.35	129	2	15	432	33	7	49	0.355
92-32	80	90	17204	3.7	6	0.1	3375	0.28	29	3	19	478	39	8	54	0.382
92-32	90	100	17205	2.6	6	0.1	2611	0.27	55	3	15	582	34	9	46	0.289
92-32	100	110	17206	4.5	6	0.1	4092	0.25	23	10	15	248	40	8	57	0.428
92-32	110	120	17207	4.5	4	0.1	7710	0.19	61	10	20	260	39	7	106	0.845
92-32	120	130	17208	2.3	1	0.1	5005	0.22	114	7	19	990	37	9	61	0.587
92-32	130	140	17209	2.3	1	0.1	4598	0.46	46	3	19	2266	40	10	50	0.513
92-32	140	150	17210	2.4	1	0.1	7432	0.77	39	4	23	2682	51	10	68	0.850
92-32	150	160	17211	3.0	1	0.1	6246	0.22	74	6	23	939	39	8	59	0.727
92-32	160	170	17212	1.8	1	0.1	3940	0.59	43	7	23	1248	37	9	43	0.455
92-32	170	180	17213	1.4	8	0.1	1964	0.49	169	7	20	797	33	8	26	0.213
92-32	180	190	17214	1.5	72	0.1	1965	0.32	157	8	19	340	42	7	24	0.211
92-32	190	200	17215	0.7	6	0.1	1396	0.40	57	3	18	1130	35	8	17	0.159
92-32	200	210	17216	0.9	3	0.1	2137	0.49	186	6	20	1336	36	8	32	0.232
92-32	210	220	17217	1.2	1	0.1	3282	0.41	56	7	18	1580	37	9	38	0.373
92-32	220	230	17218	1.2	1	0.1	5562	0.51	91	3	21	2943	45	10	53	0.605
92-32	230	240	17219	2.1	1	0.1	4957	0.42	145	5	20	2886	42	10	48	0.570
92-32	240	250	17220	1.7	1	0.1	6513	0.55	94	4	23	2871	52	11	64	0.710
92-32	250	260	17221	2.4	1	0.1	8418	0.75	64	9	24	2639	52	10	56	0.910
92-32	260	270	17222	1.5	1	0.1	5778	0.48	21	3	24	1928	48	9	40	0.640
92-32	270	280	17223	1.2	1	0.1	4023	0.42	105	2	23	1871	45	11	35	0.419
92-32	280	290	17224	0.5	1	0.1	3496	0.24	58	2	16	1452	35	8	34	0.364
92-32	290	300	17225	2.2	1	0.1	7607	0.48	114	4	25	2261	51	10	74	0.870
92-32	300	310	17226	0.1	1	0.1	5403	0.68	189	1	22	2617	47	9	61	0.637
92-32	310	320	17227	1.6	1	0.1	5722	0.53	74	1	22	2857	44	12	45	0.666
92-32	320	330	17228	1.0	1	0.1	3696	0.39	79	1	19	2765	42	14	44	0.415
92-32	330	340	17229	1.1	1	0.1	2195	0.39	18	1	18	2872	34	8	21	0.250
92-32	340	350	17230	1.6	1	0.1	2947	0.32	70	1	19	2817	35	9	29	0.332
92-32	350	360	17231	0.3	1	0.1	1656	0.45	40	1	17	2801	35	7	19	0.186
92-32	360	370	17232	0.1	1	0.1	1340	0.24	34	1	13	2502	28	10	26	0.150
92-32	370	380	17233	0.1	1	0.1	2099	0.38	79	1	16	2487	33	8	34	0.230
92-32	380	390	17234	0.2	1	0.1	1449	0.42	68	1	15	2930	30	7	18	0.165
92-32	390	400	17235	0.3	1	0.1	2652	0.41	39	1	16	3225	35	8	30	0.294

581-11

I.C.P., Au - fire geochem and Cu-assay

New Canamin Resources

Huckleberry

Min-En Laboratories
705 West 15th St.
North Vancouver, B.C.
Tel. (604) 980-5814

231-II

HOLE#	INTERVAL(feet)	SAMPL	AG	AS	CD	CU	K	MO	NI	PB	TI	ZN	W	AU	CU-ASSAY	
HOLE#	START	END	SAMPL	PPM	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPB	%	
92-33	20	30	17801	1.0	1	0.1	2957	0.29	19	4	10	1358	43	7	48	0.324
92-33	30	40	17802	0.9	1	0.1	2441	0.26	29	5	9	1288	38	9	40	0.283
92-33	40	50	17803	0.1	1	0.1	1837	0.29	80	1	7	701	40	6	17	0.208
92-33	50	60	17804	2.3	1	0.1	5705	0.34	52	7	20	1505	44	9	36	0.649
92-33	60	70	17805	0.6	1	0.1	3184	0.42	26	1	11	1618	38	8	35	0.327
92-33	70	80	17806	0.1	1	0.1	2394	0.29	46	6	9	1105	35	8	37	0.268
92-33	80	90	17807	0.1	1	0.1	1859	0.25	26	1	10	1156	36	6	30	0.207
92-33	90	100	17808	0.2	1	0.1	1974	0.27	151	2	12	1440	38	9	32	0.215
92-33	100	110	17809	0.1	1	0.1	1531	0.13	47	2	12	1123	36	7	25	0.160
92-33	110	120	17810	0.6	1	0.1	2811	0.17	152	4	11	1185	38	8	50	0.313
92-33	120	130	17811	0.1	1	0.1	1893	0.12	30	2	9	719	33	6	32	0.216
92-33	130	140	17812	0.9	1	0.1	2532	0.15	61	5	15	1283	37	8	41	0.279
92-33	140	150	17813	0.6	1	0.1	2260	0.12	70	5	9	544	39	7	25	0.265
92-33	150	160	17814	0.7	1	0.1	2640	0.16	171	3	12	821	38	9	33	0.284
92-33	160	170	17815	0.8	1	0.1	2414	0.13	88	3	13	1093	42	10	22	0.257
92-33	170	180	17816	0.9	1	0.1	2755	0.12	187	2	10	1031	38	12	33	0.313
92-33	180	190	17817	0.5	1	0.1	2821	0.13	50	2	13	501	39	8	35	0.328
92-33	190	200	17818	0.1	1	0.1	2619	0.15	36	2	15	960	38	10	35	0.308
92-33	200	210	17819	2.9	1	0.1	7784	0.26	42	1	19	1822	51	9	95	0.843
92-33	210	220	17820	2.7	1	0.1	5622	0.29	71	5	15	1530	40	8	49	0.619
92-33	220	230	17821	2.8	1	0.1	5943	0.23	39	8	19	736	38	7	93	0.686
92-33	230	240	17822	5.6	108	0.1	9607	0.32	78	4	127	546	192	9	334	1.050
92-33	240	250	17823	4.4	1	0.1	9655	0.28	125	3	22	1835	58	9	63	1.060
92-33	250	260	17824	5.1	1	0.1	10000	0.18	35	6	28	1151	69	10	150	1.340
92-33	260	270	17825	2.0	1	0.1	5828	0.36	42	1	13	1667	49	7	52	0.642
92-33	270	280	17826	5.6	1	0.1	10000	0.31	79	5	24	2049	66	10	81	1.310
92-33	280	290	17827	4.3	1	0.1	9731	0.29	39	3	16	2169	60	10	70	1.060
92-33	290	300	17828	2.0	1	0.1	6604	0.26	150	3	15	2239	49	10	52	0.743
92-33	300	310	17829	3.4	1	0.1	7016	0.64	112	1	16	2465	50	13	85	0.758
92-33	310	320	17830	2.1	1	0.1	5074	0.41	144	1	12	1447	40	6	67	0.544
92-33	320	330	17831	0.2	1	0.1	1316	0.28	104	1	4	358	20	5	10	0.137
92-33	330	340	17832	1.9	1	0.1	4290	0.35	84	1	10	1532	36	9	32	0.467
92-33	340	350	17833	2.9	1	0.1	6383	0.47	60	1	15	2628	39	8	85	0.716
92-33	350	360	17834	1.4	1	0.1	3974	0.30	65	1	10	1383	26	5	42	0.458
92-33	360	370	17835	1.8	1	0.1	5601	0.33	86	1	12	1598	39	7	63	0.623
92-33	370	380	17836	1.4	1	0.1	3116	0.41	77	1	4	2141	30	7	35	0.334

I.C.P., Au - fire geochem and Cu-assay

New Canamin Resources

Huckleberry

Min-En Laboratories
705 West 15th St.
North Vancouver, B.C.
Tel. (604) 980-5814

HOLE#	INTERVAL(feet)	SAMPL	AG	AS	CD	CU	K	MO	NI	PB	TI	ZN	W	AU	CU-ASSAY	
HOLE#	START	END	SAMPL	PPM	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPB	%	
92-33	380	390	17837	0.1	1	0.1	2649	0.76	65	1	5	2773	33	14	47	0.292
92-33	390	400	17838	0.9	1	0.1	4750	0.93	73	2	10	3379	42	10	30	0.491
92-33	400	410	17839	0.9	1	0.1	5122	0.87	89	8	8	2520	49	10	35	0.513
92-33	410	420	17840	0.1	1	0.1	3701	0.72	104	1	4	2624	42	9	27	0.354
92-33	420	430	17841	1.0	1	0.1	4406	0.93	64	1	5	2761	42	10	49	0.451
92-33	430	440	17842	0.9	1	0.1	2740	0.89	76	1	6	2679	69	9	38	0.284
92-33	440	450	17843	2.5	1	0.1	5312	0.62	114	1	19	1993	85	9	70	0.591
92-33	450	460	17844	1.1	1	0.1	2343	0.58	30	1	5	2119	33	7	20	0.255
92-33	460	470	17845	0.7	1	0.1	2066	0.47	73	1	5	1983	32	9	19	0.226
92-33	470	480	17846	0.2	1	0.1	2952	0.84	58	1	8	3058	42	12	24	0.319
92-33	480	490	17847	0.4	1	0.1	3669	0.47	116	11	12	3002	44	10	18	0.389
92-33	490	500	17848	0.1	1	0.1	99	0.21	1	98	11	3916	75	8	2	0.006

431-II

I.C.P., Au - fire geochem and Cu-assay

New Canamin Resources

Huckleberry

Min-En Laboratories
705 West 15th St.
North Vancouver, B.C.
Tel. (604) 980-5814

HOLE#	INTERVAL(feet)	SAMPL	AG	AS	CD	CU	K	MO	NI	PB	TI	ZN	W	AU	CU-ASSAY	
HOLE#	START	END	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPB	%	
92-34	40	50	17251	1.2	1	0.1	2770	1.24	18	1	1	2614	32	5	20	0.293
92-34	50	60	17252	1.1	1	0.1	3744	0.96	52	1	4	2386	31	7	34	0.399
92-34	60	70	17253	0.6	1	0.1	3616	0.78	67	1	11	2160	46	6	33	0.385
92-34	70	80	17254	1.8	1	0.1	5599	0.58	115	2	13	730	24	6	64	0.588
92-34	80	90	17255	0.1	1	0.1	2336	0.76	78	1	2	1524	28	7	27	0.238
92-34	90	100	17256	0.9	1	0.1	3267	0.49	499	2	12	602	30	7	41	0.339
92-34	100	110	17257	0.6	1	0.1	1804	0.44	32	1	6	833	28	6	14	0.187
92-34	110	120	17258	0.3	1	0.1	1447	0.40	105	1	6	483	24	7	11	0.154
92-34	120	130	17259	0.8	1	0.1	2677	0.40	256	1	8	329	25	5	36	0.289
92-34	130	140	17260	0.1	1	0.1	1733	0.49	93	1	10	706	25	5	19	0.185
92-34	140	150	17261	1.6	1	0.1	4509	0.85	97	1	9	1551	33	6	50	0.454
92-34	150	160	17262	1.1	1	0.1	3379	1.08	69	1	5	2318	33	8	28	0.325
92-34	160	170	17264	2.2	1	0.1	4156	0.61	67	1	8	1618	29	7	49	0.414
92-34	170	180	17265	2.3	1	0.1	6015	0.57	173	2	12	1515	36	9	52	0.560
92-34	180	190	17266	0.8	1	0.1	2672	0.68	47	1	9	2056	27	5	39	0.286
92-34	190	200	17267	1.3	1	0.1	3179	0.99	49	1	4	2532	30	7	53	0.344
92-34	200	210	17268	0.5	1	0.1	1434	0.68	28	1	1	2027	24	7	16	0.145
92-34	210	220	17269	0.8	1	0.1	2531	0.37	68	3	8	655	27	8	24	0.256
92-34	220	230	17270	1.9	1	0.1	5113	0.43	129	7	13	1622	32	7	45	0.506
92-34	230	240	17271	1.3	1	0.1	5384	1.82	33	12	1	3271	45	11	51	0.531
92-34	240	250	17272	2.3	1	0.1	5363	0.94	48	2	12	3153	40	10	48	0.529
92-34	250	260	17273	3.5	1	0.1	5452	0.89	65	1	10	2540	39	10	38	0.577
92-34	260	270	17274	2.2	1	0.1	4767	0.85	96	2	8	1918	43	9	36	0.473
92-34	270	280	17275	1.7	1	0.1	4816	0.98	111	1	11	2557	40	11	69	0.467
92-34	280	290	17276	1.8	1	0.1	3658	0.69	78	1	11	2502	35	8	31	0.383
92-34	290	300	17277	2.7	1	0.1	4872	0.53	301	3	14	2274	33	9	33	0.482
92-34	300	310	17278	2.0	1	0.1	3756	0.38	104	1	10	1406	33	7	29	0.380
92-34	310	320	17279	2.3	1	0.1	4344	0.48	156	1	11	2095	32	9	38	0.460
92-34	320	330	17280	1.3	1	0.1	3371	0.54	45	1	10	2225	32	8	28	0.350
92-34	330	340	17281	1.6	1	0.1	3506	0.53	41	1	9	1601	30	8	26	0.367
92-34	340	350	17282	2.1	1	0.1	4612	0.37	164	2	8	1552	30	6	38	0.508
92-34	350	360	17283	1.9	1	0.1	4210	0.51	98	1	8	2011	31	8	36	0.415
92-34	360	370	17284	1.6	1	0.1	2959	0.55	80	1	9	2144	28	7	25	0.321
92-34	370	380	17285	1.4	1	0.1	2286	0.37	82	1	11	2112	26	8	23	0.229
92-34	380	390	17286	1.7	1	0.1	2990	0.41	99	1	13	2331	27	7	27	0.314
92-34	390	400	17287	1.0	1	0.1	1776	0.40	208	1	16	1918	32	8	29	0.190

381-II

I.C.P., Au - fire geochem and Cu-assay

New Canamin Resources

Huckleberry

Min-En Laboratories
705 West 15th St.
North Vancouver, B.C.
Tel. (604) 980-5814

HOLE#	INTERVAL(feet)	SAMPL	AG	AS	CD	CU	K	MO	NI	PB	TI	ZN	W	AU	CU-ASSAY	
HOLE#	START	END	SAMPL	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPB	%	
92-34	400	410	17288	0.1	1	0.1	1042	0.29	118	2	11	842	21	5	7	0.114
92-34	410	420	17289	0.7	1	0.1	2624	0.41	116	1	12	1799	29	7	26	0.294
92-34	420	430	17290	0.3	1	0.1	2070	0.33	109	1	11	938	34	5	28	0.232
92-34	430	440	17291	1.5	1	0.1	4507	0.55	433	1	17	1426	43	7	55	0.455
92-34	440	450	17292	1.7	1	0.1	3980	0.49	120	1	14	2508	33	6	43	0.413
92-34	450	460	17293	0.9	1	0.1	2539	0.48	139	1	12	2659	31	9	58	0.256
92-34	460	470	17294	1.6	1	0.1	3708	0.29	180	1	15	1698	31	6	33	0.381
92-34	470	480	17295	1.0	1	0.1	3626	0.85	133	1	14	2715	35	10	26	0.346
92-34	480	490	17296	0.7	1	0.1	3686	0.68	147	1	3	1850	33	6	34	0.332
92-34	490	500	17297	3.0	1	0.1	2545	0.27	114	1	11	866	28	9	27	0.254

631-II

MIN-EN LABORATORIES
 705 W. 15th St.
 North Vancouver, B.C.
 Phone: 980-5814

I.C.P. and Copper assay

New Canamin Resources

Huckleberry

HOLE#	INTERVAL(feet)	SAMPLE	Cu-ASSAY	AG	AL	AS	B	BA	BE	BI	CA	CD	CO	CU	FE	K	LI	MG	
HOLE#	START	END	NAME	%	PPM	%	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	%	%	PPM	%	
92-08	310	320	40424	0.144	1.9	0.86	10	6	70	0.3	9	1.78	0.1	9	1261	1.30	0.09	9	0.90
92-08	320	330	40425	0.106	1.0	0.60	4	3	46	0.1	9	1.63	0.1	7	938	0.98	0.06	7	0.72
92-08	330	340	40426	0.112	1.2	0.60	2	3	48	0.1	9	1.63	0.1	7	970	1.05	0.06	6	0.70
92-08	340	350	40427	0.264	1.7	0.49	2	3	30	0.1	4	2.07	0.1	9	2271	1.53	0.05	5	0.81
92-08	350	360	40428	0.139	1.7	1.30	6	6	134	0.2	11	1.76	0.1	10	1217	1.67	0.10	8	0.87
92-08	360	370	40429	0.120	1.7	0.97	3	4	140	0.2	11	1.97	0.1	8	1082	1.22	0.09	5	0.71
92-08	370	380	40430	0.081	1.0	0.94	1	4	95	0.2	10	2.02	0.1	6	697	1.01	0.06	5	0.68
92-08	380	390	40431	0.096	1.5	0.82	8	5	85	0.1	12	1.67	0.1	9	863	1.08	0.09	6	0.65

061-11

MIN-EN LABORATORIES

705 W. 15th St.

North Vancouver, B.C. Huckleberry

Phone: 980-5814

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)	SAMPLE	MN	MO	NA	NI	P	PB	SB	SR	TH	TI	V	ZN	GA	SN	W	CR	
HOLE#	START	END	NAME	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	
92-08	310	320	40424	289	121	0.12	6	950	17	7	66	9	1275	44.0	30	5	3	7	87
92-08	320	330	40425	225	41	0.11	4	1030	16	6	59	6	757	31.0	25	3	2	7	86
92-08	330	340	40426	260	67	0.12	5	590	12	5	69	7	1115	40.5	26	3	2	6	86
92-08	340	350	40427	284	27	0.07	2	230	17	6	35	7	1184	51.2	29	4	2	8	90
92-08	350	360	40428	283	283	0.15	5	400	16	7	190	9	1471	53.1	26	5	3	7	82
92-08	360	370	40429	335	30	0.13	6	550	18	6	176	7	1292	39.5	26	4	2	8	120
92-08	370	380	40430	332	154	0.14	4	660	17	5	124	7	959	36.0	24	3	4	6	82
92-08	380	390	40431	353	186	0.13	2	540	17	5	97	6	1345	31.7	23	4	3	7	113

161-11

MIN-EN LABORATORIES
 705 W. 15th St.
 North Vancouver, B.C. Huckleberry
 Phone: 980-5814

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)	SAMPLE	Cu-ASSAY	AG	AL	AS	B	BA	BE	BI	CA	CD	CO	CU	FE	K	LI	MG	
HOLE#	START	END	NAME	%	PPM	%	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	%	%	PPM	%	
92-09	440	450	40418	0.054	2.4	2.97	21	10	664	0.6	17	2.90	0.1	31	463	4.45	0.18	8	2.80
92-09	450	460	40419	0.226	2.8	1.81	11	9	421	0.5	4	2.41	0.1	19	2062	3.30	0.22	11	1.82
92-09	460	470	40420	0.220	1.7	1.18	2	8	702	0.4	2	2.46	0.1	10	1870	2.45	0.34	12	1.06
92-09	470	480	40421	0.260	2.4	1.05	5	8	1687	0.5	1	3.92	0.1	10	2274	2.04	0.42	12	0.74
92-09	480	490	40422	0.257	2.1	1.12	11	10	1464	0.3	1	3.28	0.1	9	2292	1.82	0.38	18	0.85
92-09	490	500	40423	0.230	2.4	1.23	11	9	581	0.4	8	1.64	0.1	14	2008	2.59	0.45	13	1.43

261-II

MIN-EN LABORATORIES

705 W. 15th St.

North Vancouver, B.C.

Phone: 980-5814

Huckleberry

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)	SAMPLE	MN	MO	NA	NI	P	PB	SB	SR	TH	TI	V	ZN	GA	SN	W	CR	
HOLE#	START	END	NAME	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	
92-09	440	450	40418	1322	27	0.44	90	1450	26	8	311	20	2446	128.2	84	9	6	10	106
92-09	450	460	40419	762	43	0.21	38	1240	19	8	137	15	1121	91.2	52	8	4	9	115
92-09	460	470	40420	431	58	0.07	12	920	10	6	74	11	722	63.8	37	6	3	7	103
92-09	470	480	40421	532	169	0.03	9	870	22	8	157	10	647	47.8	52	6	3	6	83
92-09	480	490	40422	436	456	0.03	8	950	26	9	141	9	447	49.9	72	6	3	5	73
92-09	490	500	40423	263	592	0.08	11	980	16	6	45	13	1635	83.4	37	8	5	9	128

II-193

MIN-EN LABORATORIES
 705 W. 15th St.
 North Vancouver, B.C. Huckleberry
 Phone: 980-5814

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)		SAMPLE	Cu-ASSAY	AG	AL	AS	B	BA	BE	BI	CA	CD	CO	CU	FE	K	LI	MG
HOLE#	START	END	NAME	%	PPM	%	PPM	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	%	%	PPM	%
92-10	290	300	40432	0.247	1.4	1.54	1	6	59	0.5	5	2.06	0.1	10	2347	2.15	0.12	9	1.06
92-10	300	310	40433	0.400	2.7	3.35	2	9	227	0.7	1	2.76	0.1	14	4101	2.51	0.14	12	1.59
92-10	310	320	40434	0.349	2.1	2.88	2	8	571	0.7	1	2.43	0.1	12	3311	2.45	0.10	9	1.26
92-10	320	330	40435	0.364	2.3	2.81	2	8	286	0.6	1	2.62	0.1	11	3509	2.23	0.11	11	1.33
92-10	330	340	40436	0.440	2.6	2.00	1	6	250	0.4	1	1.87	0.1	17	4054	2.84	0.41	13	1.63
92-10	340	350	40437	0.320	2.2	1.08	1	5	215	0.2	6	1.45	0.1	16	3072	2.18	0.23	11	1.24
92-10	350	360	40438	0.495	6.4	1.16	1	7	199	0.2	2	1.25	0.1	18	4589	2.44	0.21	10	1.17
92-10	360	370	40439	0.410	2.2	1.22	1	6	181	0.3	1	1.91	0.1	13	3561	2.04	0.16	10	1.18

461-11

MIN-EN LABORATORIES

705 W. 15th St.

North Vancouver, B.C.

Phone: 980-5814

Huckleberry

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)		SAMPLE	MN	MO	NA	NI	P	PB	SB	SR	TH	TI	V	ZN	GA	SN	W	CR	
HOLE#	START	END	NAME	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM
92-10	290	300	40432	372	218	0.11	12	1060	20	11	36	12	553	95.3	31	6	4	8	97	
92-10	300	310	40433	420	396	0.17	9	1070	17	11	177	16	286	68.4	35	8	5	7	69	
92-10	310	320	40434	359	127	0.17	11	1000	15	8	279	14	331	68.7	31	7	4	6	63	
92-10	320	330	40435	391	169	0.16	7	950	17	8	232	12	451	63.4	29	7	4	7	78	
92-10	330	340	40436	352	128	0.08	12	810	15	6	44	13	1437	101.3	40	8	4	8	85	
92-10	340	350	40437	250	103	0.12	7	1070	15	7	81	9	1752	73.6	32	6	3	9	114	
92-10	350	360	40438	246	493	0.13	13	1060	17	11	117	9	1713	76.5	34	7	4	8	93	
92-10	360	370	40439	264	436	0.08	8	980	12	7	76	11	857	62.8	33	6	3	8	109	

561-11

MIN-EN LABORATORIES
 705 W. 15th St.
 North Vancouver, B.C.
 Phone: 980-5814

Huckleberry

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)		SAMPLE	Cu-ASSAY	AG	AL	AS	B	BA	BE	BI	CA	CD	CO	CU	FE	K	LI	MG
HOLE#	START	END	NAME	%	PPM	%	PPM	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	%	%	PPM	%
92-11	370	380	40409	0.270	2.4	1.27	8	8	363	0.4	7	1.48	0.1	17	2550	2.71	0.33	12	1.36
92-11	380	390	40410	0.179	1.6	1.31	1	8	235	0.4	6	1.60	0.1	14	1654	2.71	0.20	12	1.35
92-11	390	400	40411	0.265	2.2	1.58	7	9	265	0.6	5	1.79	0.1	12	2367	2.55	0.22	12	1.30
92-11	400	410	40412	0.305	2.3	2.01	3	9	340	0.5	4	2.09	0.1	14	2765	2.71	0.27	12	1.45
92-11	410	420	40413	0.364	2.7	1.97	1	10	370	0.5	5	1.82	0.1	23	3640	5.54	0.74	14	1.67
92-11	420	430	40414	0.530	2.9	2.04	1	9	384	0.5	1	1.73	0.1	21	5100	4.45	0.56	12	1.48
92-11	430	440	40415	0.526	2.5	1.33	1	6	320	0.4	1	1.19	0.1	21	4571	5.20	0.70	12	1.35
92-11	440	450	40416	0.297	2.3	1.21	5	6	370	0.4	7	1.22	0.1	17	2654	3.42	0.44	11	1.21
92-11	450	456	40417	0.364	2.6	1.20	5	7	328	0.3	8	1.08	0.1	16	3199	2.51	0.42	11	1.30

261-II

MIN-EN LABORATORIES

705 W. 15th St.

North Vancouver, B.C.

Huckleberry

I.C.P. and Copper assay

New Canamin Resources

Phone: 960-2214

HOLE#	INTERVAL(feet)		SAMPLE	MN	MO	NA	NI	P	PB	SB	SR	TH	TI	V	ZN	GA	SN	W	CR
HOLE#	START	END	NAME	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM
92-11	370	380	40409	263	182	0.12	9	990	19	9	82	14	1789	81.5	37	7	5	8	105
92-11	380	390	40410	337	156	0.09	11	1010	13	7	57	12	1124	73.5	42	6	3	7	102
92-11	390	400	40411	364	384	0.10	11	940	16	8	84	12	495	64.7	38	7	4	9	142
92-11	400	410	40412	362	246	0.13	11	1060	17	8	144	15	1021	85.3	39	8	4	7	91
92-11	410	420	40413	360	122	0.11	5	770	16	9	97	15	2358	210.2	46	11	6	13	113
92-11	420	430	40414	333	138	0.11	12	710	20	12	84	14	1615	157.3	43	9	6	10	79
92-11	430	440	40415	290	51	0.08	5	640	14	11	40	10	2085	201.8	48	10	6	10	62
92-11	440	450	40416	281	101	0.11	8	710	16	8	31	11	1943	93.7	41	7	4	8	88
92-11	450	456	40417	256	74	0.12	11	980	20	10	38	11	1891	71.2	37	7	4	9	121

261-11

MIN-EN LABORATORIES
 705 W. 15th St.
 North Vancouver, B.C. Huckleberry
 Phone: 980-5814

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)	SAMPLE	Cu-ASSAY	AG	AL	AS	B	BA	BE	BI	CA	CD	CO	CU	FE	K	LI	MG	
HOLE#	START	END	NAME	%	PPM	%	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	%	%	PPM	%	
92-12	310	320	40451	0.307	1.8	1.45	1	6	169	0.3	1	1.43	0.1	15	2750	4.19	0.33	8	0.96
92-12	320	330	40452	0.351	2.4	2.89	1	8	325	0.4	1	2.08	0.1	20	3219	4.96	0.75	12	1.75
92-12	330	340	40453	0.513	2.8	3.06	1	9	625	0.5	8	2.26	0.1	25	4771	5.61	0.76	11	1.45
92-12	340	350	40454	0.218	2.1	2.00	15	7	82	0.4	1	3.11	0.1	7	1947	1.35	0.23	6	0.52
92-12	350	360	40455	0.138	1.4	2.54	8	8	90	0.4	1	2.78	0.1	6	1266	1.31	0.21	7	0.62
92-12	360	370	40456	0.149	1.4	2.95	5	8	268	0.5	4	2.73	0.1	11	1312	2.41	0.33	8	0.84
92-12	370	380	40457	0.261	1.6	2.56	1	9	829	0.4	6	1.74	0.1	22	2642	5.89	0.81	11	1.32
92-12	380	390	40458	0.188	1.1	1.57	1	6	220	0.3	1	1.78	0.1	7	1710	1.69	0.28	8	0.67
92-12	390	400	40459	0.090	0.8	1.29	1	5	145	0.4	2	2.10	0.1	5	802	1.19	0.19	6	0.44
92-12	400	410	40460	0.067	0.5	1.12	2	4	157	0.3	2	1.64	0.1	5	563	1.21	0.19	6	0.50
92-12	410	420	40461	0.054	0.5	1.17	4	4	135	0.4	2	1.37	0.1	6	478	1.53	0.17	7	0.54
92-12	420	430	40462	0.106	0.8	1.08	1	3	111	0.3	5	1.06	0.1	9	896	1.87	0.14	8	0.63
92-12	430	440	40463	0.124	0.9	1.08	1	3	126	0.3	3	1.04	0.1	9	1065	1.76	0.14	8	0.66
92-12	440	450	40464	0.106	0.9	1.23	1	5	221	0.4	3	1.42	0.1	9	913	1.57	0.15	7	0.60
92-12	450	460	40465	0.073	1.3	5.05	1	13	798	0.5	15	2.08	0.1	23	667	4.14	1.39	21	3.12
92-12	460	470	40466	0.215	1.6	1.00	1	4	110	0.3	1	1.30	0.1	9	1866	1.64	0.14	7	0.61
92-12	470	480	40467	0.110	1.0	1.10	1	4	118	0.3	3	1.22	0.1	7	945	1.58	0.22	8	0.55
92-12	480	490	40468	0.169	1.1	1.00	1	4	97	0.2	1	1.08	0.1	9	1484	1.54	0.19	8	0.60
92-12	490	500	40469	0.098	0.6	1.04	1	3	66	0.3	1	1.09	0.1	7	872	1.41	0.12	7	0.51
92-12	500	510	40470	0.087	0.6	0.93	2	4	70	0.3	2	1.16	0.1	8	784	1.38	0.17	7	0.51
92-12	510	520	40471	0.127	0.9	0.98	1	4	80	0.2	3	1.07	0.1	9	1107	1.44	0.12	8	0.59
92-12	520	530	40472	0.170	1.1	0.94	1	3	56	0.3	1	1.29	0.1	10	1500	1.28	0.13	8	0.55
92-12	530	540	40473	0.080	0.7	1.15	6	5	69	0.3	2	1.28	0.1	8	683	1.40	0.12	7	0.53
92-12	540	550	40474	0.197	1.4	1.19	3	5	65	0.3	1	1.73	0.1	13	1741	1.37	0.16	7	0.60

861-II

MIN-EN LABORATORIES

705 W. 15th St.

North Vancouver, B.C. Huckleberry

Phone: 980-5814

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)		SAMPLE	MN	MO	NA	NI	P	PB	SB	SR	TH	TI	V	ZN	GA	SN	W	CR
HOLE#	START	END	NAME	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM
92-12	310	320	40451	292	46	0.05	1	970	4	5	27	4	803	49.6	38	6	4	4	52
92-12	320	330	40452	834	27	0.16	15	810	24	25	33	8	1443	141.0	71	9	5	11	125
92-12	330	340	40453	589	96	0.08	9	670	9	10	44	8	1600	208.2	56	9	6	10	56
92-12	340	350	40454	432	75	0.07	3	250	24	22	15	4	106	24.8	56	4	1	4	73
92-12	350	360	40455	297	132	0.09	2	260	9	6	15	5	171	20.7	24	5	2	3	47
92-12	360	370	40456	326	30	0.10	5	360	9	6	34	6	620	72.9	34	6	2	6	75
92-12	370	380	40457	400	177	0.09	2	800	4	5	36	7	2187	204.0	41	10	6	9	61
92-12	380	390	40458	254	230	0.09	3	240	5	4	30	4	414	38.6	23	4	3	4	63
92-12	390	400	40459	255	87	0.07	4	240	8	3	35	4	125	15.7	19	3	1	2	55
92-12	400	410	40460	262	43	0.08	2	200	6	2	40	4	159	14.7	22	3	1	4	70
92-12	410	420	40461	275	41	0.10	3	220	4	2	55	3	290	18.2	27	3	1	5	109
92-12	420	430	40462	272	41	0.09	1	320	7	3	62	2	818	27.9	29	4	2	4	59
92-12	430	440	40463	262	41	0.09	3	310	10	4	38	3	588	27.0	29	4	2	5	92
92-12	440	450	40464	249	36	0.13	2	260	6	3	43	3	409	26.1	28	4	2	4	65
92-12	450	460	40465	426	13	0.41	6	710	2	5	90	12	2884	207.9	35	13	6	11	72
92-12	460	470	40466	254	104	0.08	3	280	8	5	31	3	246	25.9	30	3	1	3	54
92-12	470	480	40467	301	20	0.08	2	280	15	3	25	2	395	21.4	31	3	2	2	56
92-12	480	490	40468	256	36	0.09	2	270	8	4	32	3	385	20.8	29	3	1	4	64
92-12	490	500	40469	226	34	0.10	1	230	7	3	25	2	268	16.4	27	2	1	2	44
92-12	500	510	40470	245	100	0.08	3	240	8	4	24	3	227	15.4	26	2	2	4	81
92-12	510	520	40471	232	55	0.09	1	260	6	4	28	3	541	18.7	33	3	2	3	57
92-12	520	530	40472	221	28	0.08	2	260	11	5	23	2	228	16.3	30	3	1	4	75
92-12	530	540	40473	260	35	0.10	1	210	11	4	25	4	232	18.1	29	4	1	4	67
92-12	540	550	40474	238	53	0.08	3	230	11	5	22	4	115	21.3	29	3	1	4	71

561-11

MIN-EN LABORATORIES
 705 W. 15th St.
 North Vancouver, B.C.
 Phone: 980-5814

Huckleberry

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL (feet)	SAMPLE	Cu-ASSAY	AG	AL	AS	B	BA	BE	BI	CA	CD	CO	CU	FE	K	LI	MG	
HOLE#	START	END	NAME	%	PPM	%	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	%	%	PPM	%	
93-01	40	50	17301	0.457	2.1	1.40	1	5	144	0.7	11	1.43	0.1	18	3961	5.81	0.23	8	1.08
93-01	50	60	17302	0.557	3.2	1.78	1	5	145	0.7	12	2.03	0.1	20	4714	5.18	0.36	8	1.24
93-01	60	70	17303	0.436	2.4	2.54	1	7	208	0.6	13	1.98	0.1	27	3914	5.59	0.46	10	1.59
93-01	70	80	17304	0.194	1.6	1.48	1	4	135	0.4	16	1.33	0.1	26	1711	6.38	0.26	8	1.15
93-01	80	90	17305	0.465	2.9	2.27	1	7	391	0.5	18	1.42	0.1	30	4301	6.13	0.70	10	1.56
93-01	90	100	17306	0.349	1.3	1.44	1	5	274	0.4	3	1.26	0.1	24	2844	6.22	0.42	8	1.26
93-01	100	110	17307	0.460	2.2	2.53	1	9	352	0.4	7	1.83	0.1	20	3613	5.58	0.70	12	2.03
93-01	110	120	17308	0.594	2.9	1.80	1	6	191	0.4	20	1.34	0.1	24	5309	6.76	0.44	8	1.29
93-01	120	130	17309	0.542	2.8	1.59	1	7	193	0.3	5	1.30	0.1	30	4552	6.62	0.39	8	1.16
93-01	130	140	17310	0.564	3.2	1.87	1	8	139	0.4	6	1.90	0.1	28	4912	6.88	0.35	11	1.51
93-01	140	150	17311	0.682	3.8	1.71	1	8	185	0.2	6	1.39	0.1	38	5867	6.31	0.43	9	1.44
93-01	150	160	17312	0.388	4.8	1.93	48	9	128	0.4	5	2.69	0.1	22	3713	5.51	0.38	9	1.12
93-01	160	170	17313	0.313	2.3	3.52	1	14	405	0.5	11	1.85	0.1	26	2943	6.32	0.65	12	1.93
93-01	170	180	17314	0.278	2.6	3.69	1	15	342	0.5	7	2.17	0.1	17	2708	4.62	0.60	12	1.50
93-01	180	190	17315	0.632	4.0	3.42	1	15	485	0.5	8	1.82	0.1	24	5556	5.23	0.59	10	1.51
93-01	190	200	17316	0.257	1.5	4.85	1	18	443	0.4	9	2.42	0.1	21	2498	5.78	0.70	10	1.51
93-01	200	210	17317	0.188	0.9	3.53	1	15	169	0.4	10	2.14	0.1	21	1776	5.80	0.23	7	0.91
93-01	210	220	17318	0.463	3.1	2.36	1	13	708	0.4	6	1.50	0.1	18	4115	4.86	0.63	11	1.34
93-01	220	230	17319	0.910	4.7	1.33	1	10	147	0.3	1	1.77	0.1	21	8209	4.73	0.17	7	0.68
93-01	230	240	17320	0.526	2.7	1.29	1	10	107	0.4	1	1.49	0.1	15	4402	4.64	0.17	8	0.80
93-01	240	250	17321	0.284	2.0	1.19	1	9	211	0.3	4	1.21	0.1	16	2565	4.75	0.27	9	0.86
93-01	250	260	17322	0.293	2.3	1.35	1	10	170	0.3	5	1.33	0.1	16	2656	4.37	0.29	8	0.82
93-01	260	270	17323	0.675	4.2	1.53	1	10	94	0.3	4	1.56	0.1	18	5951	4.35	0.18	9	0.84
93-01	270	280	17324	0.451	3.4	1.32	1	10	103	0.2	9	1.19	0.1	18	4016	4.65	0.22	9	0.90
93-01	280	290	17325	0.582	3.5	1.41	1	9	126	0.3	3	1.73	0.1	17	4869	3.80	0.24	8	0.87
93-01	290	300	17326	0.500	3.4	2.27	1	12	225	0.5	4	1.74	0.1	20	4522	4.44	0.44	11	1.53
93-01	300	310	17327	0.389	2.9	1.40	1	9	134	0.3	3	1.42	0.1	16	3649	3.92	0.29	10	1.02
93-01	310	320	17328	0.403	3.5	1.44	1	10	216	0.3	10	1.32	0.1	18	3935	4.58	0.37	9	0.96
93-01	320	330	17329	0.350	3.1	3.53	1	14	738	0.4	23	1.59	0.1	22	3398	5.33	1.11	14	2.00
93-01	330	340	17330	0.281	2.3	2.12	3	11	365	0.3	4	1.40	0.1	13	2922	2.67	0.45	12	1.01
93-01	340	350	17331	0.116	2.6	2.63	6	8	318	0.6	8	1.92	0.1	16	2223	3.72	0.25	18	1.29
93-01	350	360	17332	0.168	1.5	1.26	10	3	113	0.3	3	1.39	0.1	9	1618	1.71	0.20	9	0.73
93-01	360	370	17333	0.215	1.9	1.49	3	3	144	0.3	3	1.22	0.1	11	2203	1.90	0.26	12	0.91
93-01	370	380	17334	0.294	2.0	1.27	4	3	72	0.3	1	1.22	0.1	9	2743	1.69	0.15	10	0.71
93-01	380	390	17335	0.305	2.4	1.29	2	3	97	0.3	5	1.08	0.1	12	2899	2.13	0.17	10	0.76
93-01	390	400	17336	0.501	3.1	1.35	3	3	79	0.3	1	1.54	0.1	11	4818	1.85	0.21	9	0.69
93-01	400	410	17337	0.347	2.6	1.21	10	3	93	0.3	3	1.05	0.1	12	3495	1.83	0.18	9	0.69
93-01	410	420	17338	0.234	1.9	1.13	6	2	72	0.3	5	0.96	0.1	12	2103	1.88	0.13	8	0.66

002-11

MIN-EN LABORATORIES
 705 W. 15th St.
 North Vancouver, B.C.
 Phone: 980-5814

I.C.P. and Copper assay

New Canamin Resources

Huckleberry

HOLE#	INTERVAL(feet)		SAMPLE	MN	MO	NA	NI	P	PB	SB	SR	TH	TI	V	ZN	GA	SN	W	CR
HOLE#	START	END	NAME	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM
93-01	40	50	17301	422	164	0.05	1	760	13	7	42	4	1547	135.8	53	7	2	8	81
93-01	50	60	17302	496	67	0.08	1	750	17	9	37	3	1528	138.8	53	7	2	10	107
93-01	60	70	17303	463	11	0.20	10	700	15	8	83	3	1914	162.2	44	8	3	10	103
93-01	70	80	17304	516	22	0.08	1	680	12	3	76	2	3110	166.5	41	7	1	9	89
93-01	80	90	17305	502	28	0.16	1	580	12	8	164	3	3069	192.0	40	8	2	9	62
93-01	90	100	17306	368	12	0.07	1	700	13	5	96	6	1412	208.0	50	7	3	8	47
93-01	100	110	17307	530	41	0.12	1	610	13	7	62	9	2095	219.2	60	10	4	13	120
93-01	110	120	17308	605	119	0.10	1	880	12	9	92	3	3196	193.5	61	8	2	10	77
93-01	120	130	17309	428	53	0.10	1	880	13	6	79	6	2323	190.7	48	8	3	10	76
93-01	130	140	17310	729	16	0.07	1	900	13	9	46	8	2630	214.8	55	9	4	10	75
93-01	140	150	17311	750	29	0.09	1	690	14	10	93	7	2622	217.7	56	9	4	11	86
93-01	150	160	17312	1120	66	0.08	1	680	42	224	62	5	1548	198.7	159	8	3	9	61
93-01	160	170	17313	978	65	0.31	1	620	16	13	94	9	2848	243.2	52	12	4	13	111
93-01	170	180	17314	821	118	0.33	1	520	20	9	114	10	1716	138.9	43	10	4	9	76
93-01	180	190	17315	417	55	0.32	1	440	18	11	62	8	2389	171.4	59	10	3	12	111
93-01	190	200	17316	435	10	0.64	1	450	18	11	83	10	2306	273.2	46	13	4	12	80
93-01	200	210	17317	494	9	0.41	1	640	14	9	94	7	1955	270.8	37	10	3	12	102
93-01	210	220	17318	407	58	0.17	1	670	14	8	65	8	1803	124.6	44	8	3	8	61
93-01	220	230	17319	340	33	0.04	1	960	16	14	20	5	636	68.5	52	5	2	7	59
93-01	230	240	17320	265	48	0.05	1	790	10	8	20	5	527	66.2	39	5	1	6	54
93-01	240	250	17321	282	25	0.04	1	880	6	5	18	5	1119	70.4	41	6	2	6	67
93-01	250	260	17322	360	69	0.05	1	860	11	5	22	6	1139	69.4	39	6	2	6	58
93-01	260	270	17323	396	17	0.05	1	980	13	11	37	5	1133	73.6	43	6	2	7	67
93-01	270	280	17324	314	25	0.05	1	920	12	7	15	6	2280	70.8	41	6	2	9	90
93-01	280	290	17325	299	48	0.03	1	880	14	10	15	6	991	64.3	42	6	1	7	61
93-01	290	300	17326	393	35	0.07	7	950	14	9	36	8	1333	85.9	52	8	3	10	96
93-01	300	310	17327	338	58	0.05	1	990	8	7	42	5	1001	47.2	43	6	2	6	72
93-01	310	320	17328	363	41	0.05	1	1040	13	8	38	6	1849	48.7	50	7	2	8	79
93-01	320	330	17329	369	11	0.31	8	1060	15	8	139	9	2927	172.7	45	11	3	11	103
93-01	330	340	17330	289	87	0.21	6	360	12	6	65	6	1327	90.4	38	7	2	10	146
93-01	340	350	17331	450	252	0.21	13	680	18	7	95	9	1740	66.2	63	9	3	11	148
93-01	350	360	17332	281	46	0.08	4	360	10	4	48	6	550	32.4	33	4	1	6	99
93-01	360	370	17333	273	42	0.10	4	420	11	5	36	5	878	36.9	37	5	1	6	90
93-01	370	380	17334	249	87	0.06	4	380	12	6	36	5	398	30.3	38	4	1	5	85
93-01	380	390	17335	264	49	0.08	3	380	12	6	41	6	1121	35.6	42	5	2	8	112
93-01	390	400	17336	248	60	0.07	6	440	16	10	36	5	465	30.0	42	5	2	6	87
93-01	400	410	17337	243	98	0.08	6	340	15	7	40	4	908	31.1	40	4	2	8	129
93-01	410	420	17338	256	51	0.08	3	280	11	4	28	5	1047	28.4	41	4	1	8	111

102-II

MIN-EN LABORATORIES
 705 W. 15th St.
 North Vancouver, B.C.
 Phone: 980-5814

Huckleberry

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)	SAMPLE	Cu-ASSAY	AG	AL	AS	B	BA	BE	BI	CA	CD	CO	CU	FE	K	LI	MG	
HOLE#	START	END	NAME	%	PPM	%	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	%	%	PPM	%	
93-01	420	430	17339	0.365	2.8	1.21	11	3	75	0.3	5	1.00	0.1	13	3372	2.10	0.14	8	0.68
93-01	430	440	17340	0.895	5.2	1.68	2	4	104	0.3	1	1.35	0.1	17	8233	2.69	0.20	9	0.68
93-01	440	450	17341	0.964	5.1	1.53	7	4	86	0.2	1	1.45	0.1	14	8405	2.43	0.17	7	0.61
93-01	450	460	17342	0.331	2.6	1.45	2	4	116	0.4	5	1.23	0.1	11	3208	2.43	0.19	8	0.67

202-II

MIN-EN LABORATORIES

705 W. 15th St.

North Vancouver, B.C.

Huckleberry

Phone: 980-5814

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)	SAMPLE	MN	MO	NA	NI	P	PB	SB	SR	TH	TI	V	ZN	GA	SN	W	CR	
HOLE#	START	END	NAME	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	
93-01	420	430	17339	261	55	0.08	4	320	13	6	38	5	1279	30.6	42	5	2	8	110
93-01	430	440	17340	250	99	0.14	4	510	19	14	85	5	1011	36.8	47	5	2	8	108
93-01	440	450	17341	232	209	0.11	4	460	19	15	51	5	831	34.1	47	4	2	9	126
93-01	450	460	17342	305	113	0.11	4	300	11	6	30	5	1121	38.8	39	6	2	8	98

II-203

MIN-EN LABORATORIES

705 W. 15th St.

North Vancouver, B.C.

Huckleberry

Phone: 980-5814

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)	SAMPLE	Cu-ASSAY	AG	AL	AS	B	BA	BE	BI	CA	CD	CO	CU	FE	K	LI	MG	
HOLE#	START	END	NAME	%	PPM	%	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	%	%	PPM	%	
93-02	60	70	17351	0.665	6.0	2.19	187	6	1580	0.4	2	3.90	0.1	15	6459	2.82	0.92	11	1.57
93-02	70	80	17352	1.661	7.3	4.95	16	13	806	0.5	14	2.09	0.1	29	10000	5.38	1.43	19	4.54
93-02	80	90	17353	0.742	3.4	5.18	2	12	450	0.6	9	2.10	0.1	26	7010	5.31	1.41	18	4.15
93-02	90	100	17354	0.270	1.9	1.30	2	2	160	0.2	6	0.92	0.1	11	2416	1.86	0.38	12	1.27
93-02	100	110	17355	0.252	1.6	1.20	7	1	161	0.3	4	0.86	0.1	9	2445	1.93	0.40	12	1.06
93-02	110	120	17356	0.213	1.8	5.17	15	12	576	0.7	16	1.53	0.1	28	2095	5.58	1.88	24	4.59
93-02	120	130	17357	0.164	1.7	6.06	19	15	633	0.7	17	2.18	0.1	27	1539	6.58	1.69	18	4.17
93-02	130	140	17358	0.320	2.6	1.98	7	3	184	0.4	7	2.02	0.1	13	3068	2.59	0.69	11	1.53
93-02	140	150	17359	0.522	3.3	1.88	5	3	177	0.3	4	2.10	0.1	14	4992	2.36	0.69	12	1.75
93-02	150	160	17360	0.354	2.5	1.54	4	2	121	0.3	5	1.78	0.1	12	3376	2.19	0.42	10	1.20
93-02	160	170	17361	0.395	2.7	2.30	10	4	299	0.4	7	2.33	0.1	16	3662	2.84	0.99	12	1.96
93-02	170	180	17362	0.348	2.8	1.87	8	2	290	0.4	6	1.74	0.1	11	3478	2.26	0.45	13	1.38
93-02	180	190	17363	0.188	1.5	1.17	4	2	192	0.4	7	1.08	0.1	8	1703	1.85	0.19	8	0.81
93-02	190	200	17364	0.132	1.2	1.21	6	3	234	0.3	7	1.03	0.1	8	1233	1.70	0.26	9	0.88
93-02	200	210	17365	0.347	2.5	1.37	14	3	573	0.5	3	1.74	0.1	8	3269	1.56	0.32	9	0.81
93-02	210	220	17366	0.384	3.2	2.64	1	7	759	0.5	14	1.80	0.1	22	3781	4.68	0.71	12	2.21
93-02	220	230	17367	0.455	3.3	3.21	1	8	1082	0.3	17	1.84	0.1	30	4895	7.37	1.15	14	2.48
93-02	230	240	17368	0.960	4.4	3.17	1	8	633	0.4	9	1.98	0.1	29	8814	5.96	1.02	13	2.32
93-02	240	250	17369	1.450	5.7	2.12	1	6	434	0.2	8	2.39	0.1	25	10000	4.99	0.94	13	1.83
93-02	250	260	17370	0.411	3.4	1.72	8	4	947	0.3	13	2.76	0.1	18	3974	3.40	0.73	11	1.31
93-02	260	270	17371	0.350	3.3	2.00	1	6	698	0.4	17	2.29	0.1	16	3112	3.49	0.93	17	1.65
93-02	270	280	17372	0.618	3.1	2.43	1	7	488	0.3	8	1.56	0.1	23	5667	5.25	1.21	16	2.16
93-02	280	290	17373	0.562	2.9	3.06	1	10	444	0.4	14	1.44	0.1	28	5156	6.81	1.07	16	2.44
93-02	290	300	17374	0.394	3.0	3.04	1	9	356	0.4	14	1.53	0.1	27	3892	7.67	0.94	13	2.14
93-02	300	310	17375	0.595	3.9	1.71	1	7	170	0.4	7	1.52	0.1	16	5652	3.46	0.43	11	1.33
93-02	310	320	17376	0.545	2.6	2.50	1	8	340	0.3	13	1.94	0.1	24	5119	7.41	0.80	11	1.73
93-02	320	330	17377	0.275	0.6	2.54	1	7	160	0.3	14	1.81	0.1	23	2559	7.96	0.46	6	1.09
93-02	330	340	17378	0.840	4.2	4.84	1	14	601	0.5	17	2.97	0.1	28	7143	6.91	0.93	15	2.78
93-02	340	350	17379	0.349	1.5	3.62	1	10	222	0.4	15	2.34	0.1	22	2987	7.12	0.49	8	1.30
93-02	350	360	17380	0.458	2.4	4.51	1	12	397	0.4	17	2.63	0.1	26	4247	7.79	0.68	11	1.75
93-02	360	370	17381	0.307	0.3	1.96	1	6	193	0.3	12	1.25	0.1	26	2823	8.12	0.65	9	1.54
93-02	370	380	17382	0.352	0.4	1.70	1	6	285	0.3	12	1.88	0.1	28	2993	8.47	0.72	9	1.53
93-02	380	390	17383	0.667	2.1	1.50	1	6	243	0.1	10	1.86	0.1	25	6248	7.10	0.94	11	1.63
93-02	390	400	17384	0.887	1.9	1.32	1	8	197	0.1	13	1.85	0.1	23	7759	7.24	0.79	9	1.39
93-02	400	410	17385	0.624	2.0	1.68	1	9	257	0.2	16	1.81	0.1	28	5675	7.84	1.02	12	1.89
93-02	410	420	17386	1.025	5.1	1.94	1	14	345	0.1	19	2.75	0.1	28	9196	6.53	1.13	12	2.20
93-02	420	430	17387	0.480	0.1	1.99	1	10	285	0.1	18	1.75	0.1	29	4484	8.33	0.96	12	1.71
93-02	430	440	17388	0.442	3.6	2.65	1	12	340	0.3	12	2.42	0.1	20	4168	4.37	0.69	10	1.22

A02-7

MIN-EN LABORATORIES

705 W. 15th St.

North Vancouver, B.C.

Phone: 980-5814

Huckleberry

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)		SAMPLE	MN	MO	NA	NI	P	PB	SB	SR	TH	TI	ZN	GA	SN	W	CR	
HOLE#	START	END	NAME	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	
93-02	60	70	17351	1208	85	0.10	18	610	193	93	43	6	1058	122.5	468	7	2	12	177
93-02	70	80	17352	667	123	0.19	35	780	33	29	50	12	2800	292.2	59	12	4	24	311
93-02	80	90	17353	491	183	0.26	27	730	21	18	48	12	2857	288.0	46	13	5	21	261
93-02	90	100	17354	191	37	0.07	5	420	10	5	15	5	1446	55.0	34	6	2	7	89
93-02	100	110	17355	221	30	0.09	8	370	10	5	12	5	831	47.1	36	5	2	9	136
93-02	110	120	17356	505	39	0.29	45	840	15	11	105	13	3589	294.0	50	14	5	27	381
93-02	120	130	17357	536	6	0.51	52	840	17	14	84	12	3805	299.7	50	14	5	29	412
93-02	130	140	17358	253	75	0.22	14	380	10	6	32	7	1573	87.8	37	7	2	13	197
93-02	140	150	17359	221	13	0.17	19	410	14	9	29	7	1567	81.8	39	7	2	11	166
93-02	150	160	17360	203	57	0.17	15	360	9	5	27	5	1463	58.7	34	6	2	10	146
93-02	160	170	17361	239	156	0.22	23	510	14	8	38	8	1931	107.5	35	9	3	14	207
93-02	170	180	17362	309	47	0.13	11	350	14	7	23	6	1465	63.3	40	7	3	11	163
93-02	180	190	17363	234	25	0.07	5	250	9	4	12	5	1033	30.7	34	4	2	6	91
93-02	190	200	17364	289	49	0.06	7	300	9	3	13	5	1040	33.1	34	5	2	7	112
93-02	200	210	17365	467	104	0.04	6	310	28	15	16	5	504	23.7	84	4	1	6	81
93-02	210	220	17366	403	121	0.12	29	1080	16	8	46	10	3347	153.3	53	11	4	13	153
93-02	220	230	17367	506	54	0.19	28	1270	19	8	62	10	4527	296.5	56	13	5	17	158
93-02	230	240	17368	426	51	0.09	12	790	21	15	41	10	3205	267.5	54	12	5	15	132
93-02	240	250	17369	274	101	0.08	16	710	24	18	27	8	2921	297.3	42	10	5	14	87
93-02	250	260	17370	387	177	0.09	8	900	16	10	44	8	1790	85.8	34	7	4	9	108
93-02	260	270	17371	389	169	0.05	5	750	16	6	28	7	1976	101.8	34	8	3	9	89
93-02	270	280	17372	296	73	0.12	3	660	18	10	21	8	2929	246.5	36	12	4	13	106
93-02	280	290	17373	538	199	0.12	3	590	16	11	27	10	3946	363.9	52	13	4	15	87
93-02	290	300	17374	527	163	0.16	1	650	19	8	65	10	3860	427.4	48	13	5	15	86
93-02	300	310	17375	308	363	0.05	5	1340	19	9	21	8	2156	133.5	38	8	3	10	93
93-02	310	320	17376	440	56	0.16	1	820	16	10	101	9	3605	383.0	43	13	4	15	87
93-02	320	330	17377	473	31	0.22	1	640	12	7	85	7	3337	426.7	39	11	4	15	114
93-02	330	340	17378	609	60	0.14	1	710	21	18	313	11	4227	389.2	51	16	5	15	68
93-02	340	350	17379	511	91	0.23	1	550	17	10	100	9	3122	365.5	41	13	4	15	114
93-02	350	360	17380	561	32	0.25	1	680	20	13	265	9	3843	396.7	48	15	5	15	77
93-02	360	370	17381	539	120	0.11	1	600	6	4	54	7	3455	449.7	42	11	4	15	92
93-02	370	380	17382	503	84	0.11	1	600	14	6	21	8	2883	428.2	52	12	4	15	80
93-02	380	390	17383	384	48	0.10	1	640	7	9	26	1	2831	398.6	49	9	3	11	68
93-02	390	400	17384	338	57	0.09	1	630	15	10	26	1	2813	408.5	53	9	3	11	77
93-02	400	410	17385	474	45	0.10	1	660	12	8	30	1	3315	397.2	51	9	3	12	84
93-02	410	420	17386	1160	760	0.07	1	760	27	14	45	1	3203	362.6	67	10	4	11	80
93-02	420	430	17387	524	24	0.09	1	610	9	9	41	1	3397	800.9	49	12	3	18	109
93-02	430	440	17388	487	86	0.16	1	590	13	9	78	3	2063	103.4	39	7	2	9	128

- 502 - II

I.C.P. and Copper assay

New Canamin Resources

Huckleberry

HOLE#	INTERVAL(feet)	SAMPLE	Cu-ASSAY	AG	AL	AS	B	BA	BE	BI	CA	CD	CO	CU	FE	K	LI	MG	
HOLE#	START	END	NAME	%	PPM	%	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	%	%	PPM	%	
93-02	440	450	17389	0.381	3.1	2.11	1	5	384	0.2	11	1.53	0.1	19	3533	4.42	0.74	11	1.37
93-02	450	460	17390	0.345	2.5	1.69	1	5	159	0.3	7	1.47	0.1	12	3069	3.08	0.38	10	1.05
93-02	460	470	17391	0.443	2.3	1.38	1	4	152	0.4	2	1.67	0.1	12	4102	2.95	0.63	9	0.91
93-02	470	480	17392	0.312	2.3	1.28	1	4	158	0.3	9	1.00	0.1	14	2788	3.59	0.39	10	0.99
93-02	480	490	17393	0.386	2.2	1.83	1	3	248	0.3	5	1.02	0.1	20	3727	4.50	0.68	12	1.39
93-02	490	500	17394	0.478	2.8	1.31	1	2	71	0.3	4	1.30	0.1	14	4170	3.14	0.19	8	0.78
93-02	500	510	17395	0.553	3.3	1.16	1	3	116	0.2	3	1.29	0.1	14	5036	3.30	0.26	9	0.95
93-02	510	520	17396	0.431	3.1	1.64	1	4	74	0.3	6	1.59	0.1	15	3791	3.59	0.24	9	1.00
93-02	520	530	17397	0.534	3.7	4.60	6	12	443	0.4	16	1.86	0.1	26	4600	6.23	1.34	17	3.08
93-02	530	540	17398	0.446	2.3	3.32	1	9	492	0.4	14	1.23	0.1	30	4148	7.94	1.45	19	3.09
93-02	540	550	17399	0.897	4.1	2.79	1	15	424	0.6	12	1.35	0.1	32	7703	9.22	1.03	15	2.09
93-02	550	560	17400	0.945	4.8	2.23	1	8	349	0.4	6	1.19	0.1	26	8505	8.49	0.93	15	1.78
93-02	560	570	17401	1.176	5.9	2.51	1	9	361	0.5	8	1.32	0.1	25	9159	6.68	0.91	14	2.17
93-02	570	580	17402	0.534	3.5	2.78	1	9	462	0.5	10	1.58	0.1	27	5030	7.88	1.14	17	2.21
93-02	580	590	17403	0.485	2.6	2.58	1	8	526	0.5	11	1.43	0.1	26	4386	7.40	1.14	16	2.18
93-02	590	600	17404	0.334	1.8	2.34	1	7	501	0.5	13	1.07	0.1	25	2911	7.82	1.16	16	2.09
93-02	600	610	17405	0.335	2.3	2.19	1	7	507	0.4	11	1.26	0.1	20	2640	5.05	0.90	13	1.88
93-02	610	620	17406	0.320	2.5	1.92	5	6	445	0.5	7	1.96	0.1	13	2777	3.41	0.53	9	1.13
93-02	620	630	17407	0.552	3.4	2.61	3	8	389	0.5	7	2.14	0.1	17	4663	3.84	0.73	11	1.53
93-02	630	640	17408	0.835	4.3	3.41	1	10	232	0.5	2	2.79	0.1	21	7146	4.87	0.44	14	1.67
93-02	640	650	17409	0.550	2.5	2.87	1	9	283	0.6	8	1.80	0.1	24	4638	6.26	0.65	16	2.23

HOLE#	INTERVAL(feet)	SAMPLE	AU
HOLE#	START	END	NAME
93-02	380	390	17383
93-02	390	400	17384
93-02	400	410	17385
93-02	410	420	17386
93-02	420	430	17387
93-02	430	440	17388

II-206

MIN-EN LABORATORIES
 705 W. 15th St.
 North Vancouver, B.C. Huckleberry
 Phone: 980-5814

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)	SAMPLE	MN	MO	NA	NI	P	PB	SB	SR	TH	TI	V	ZN	GA	SN	W	CR	
HOLE#	START	END	NAME	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	
93-02	440	450	17389	426	71	0.16	1	570	14	6	43	7	2721	110.9	46	9	3	9	92
93-02	450	460	17390	425	193	0.13	3	580	8	6	43	7	1553	91.9	41	7	2	8	71
93-02	460	470	17391	672	150	0.05	5	410	20	8	23	6	852	80.0	41	5	2	7	77
93-02	470	480	17392	433	177	0.07	2	300	14	5	22	5	1898	79.4	44	6	3	7	75
93-02	480	490	17393	310	92	0.14	2	450	10	6	39	6	2229	152.1	46	8	4	9	86
93-02	490	500	17394	309	65	0.11	2	670	11	7	43	5	1545	86.5	37	5	2	7	72
93-02	500	510	17395	306	171	0.07	4	900	14	8	39	5	1526	84.5	41	6	3	8	80
93-02	510	520	17396	325	137	0.16	8	780	15	8	28	6	1789	99.5	42	7	3	11	135
93-02	520	530	17397	514	102	0.31	41	640	18	14	92	13	3750	238.7	53	13	6	21	262
93-02	530	540	17398	501	57	0.19	14	710	11	9	57	12	3816	327.8	61	14	6	21	248
93-02	540	550	17399	480	1336	0.13	3	450	24	16	76	12	3664	335.0	63	15	8	16	100
93-02	550	560	17400	423	242	0.13	1	410	19	14	52	8	3064	344.8	59	13	6	15	95
93-02	560	570	17401	491	242	0.12	3	560	22	16	53	10	2949	320.8	57	12	5	15	90
93-02	570	580	17402	503	183	0.15	1	520	16	11	59	11	3086	363.6	57	14	6	15	102
93-02	580	590	17403	524	102	0.11	1	450	15	8	34	10	3246	323.2	55	12	5	13	85
93-02	590	600	17404	472	61	0.11	1	410	12	6	28	10	3489	343.5	49	13	5	14	102
93-02	600	610	17405	399	90	0.07	5	530	11	6	24	9	2702	208.0	40	10	3	10	75
93-02	610	620	17406	311	158	0.07	6	440	15	13	27	7	1215	101.4	41	7	2	8	77
93-02	620	630	17407	316	117	0.08	6	490	41	27	34	9	1775	143.4	59	9	3	9	65
93-02	630	640	17408	463	108	0.17	14	590	22	16	74	9	1301	209.5	55	10	4	10	65
93-02	640	650	17409	544	99	0.19	10	580	18	10	98	11	2286	293.3	58	11	5	15	122

II-207

MIN-EN LABORATORIES
 705 W. 15th St.
 North Vancouver, B.C. Huckleberry
 Phone: 980-5814

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)	SAMPLE	Cu-ASSAY	AG	AL	AS	B	BA	BE	BI	CA	CD	CO	CU	FE	K	LI	MG	
HOLE#	START	END	NAME	%	PPM	%	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	%	%	PPM	%	
93-03	30	40	17451	0.204	1.2	1.68	1	5	144	0.6	7	5.04	0.1	13	1740	3.97	0.34	9	0.85
93-03	40	50	17452	0.190	0.9	2.49	1	8	251	0.6	8	3.83	0.1	18	1794	5.69	0.64	11	1.40
93-03	50	60	17453	0.270	2.1	1.80	6	7	140	0.4	8	5.26	0.1	11	2573	2.69	0.36	8	0.71
93-03	60	70	17454	0.474	2.9	1.59	2	6	222	0.5	10	2.69	0.1	15	4359	4.29	0.39	7	0.78
93-03	70	80	17455	0.318	1.8	1.07	1	4	68	0.5	7	2.38	0.1	15	2919	4.88	0.16	5	0.49
93-03	80	90	17456	0.316	2.8	1.46	1	5	105	0.7	7	2.06	0.1	12	3052	5.07	0.32	8	0.81
93-03	90	100	17457	0.399	2.6	1.82	3	8	136	0.5	11	1.82	0.1	16	3932	4.73	0.31	10	1.29
93-03	100	110	17458	0.504	3.4	1.91	1	7	251	0.4	10	1.55	0.1	17	5098	4.39	0.55	12	1.44
93-03	110	120	17459	0.247	1.6	3.72	1	13	410	0.6	15	2.32	0.1	25	2371	5.42	0.90	14	3.46
93-03	120	130	17460	0.546	3.4	2.27	5	9	200	0.4	15	2.29	0.1	17	5089	4.51	0.45	10	1.67
93-03	130	140	17461	0.231	1.8	1.44	2	6	198	0.6	10	1.72	0.1	14	2031	5.21	0.45	9	1.17
93-03	140	150	17462	0.625	3.6	1.30	2	5	200	0.5	14	1.46	0.1	16	5573	4.68	0.38	9	1.09
93-03	150	160	17463	0.270	2.4	1.21	1	5	207	0.4	15	1.15	0.1	17	2576	5.47	0.31	8	1.12
93-03	160	170	17464	0.419	2.5	1.14	1	5	156	0.4	12	1.18	0.1	16	3841	4.40	0.33	9	1.01
93-03	170	180	17465	0.274	2.0	1.93	1	7	963	0.3	16	0.97	0.1	20	2535	6.18	0.92	11	1.54
93-03	180	190	17466	0.451	2.1	2.20	1	9	531	0.3	20	1.31	0.1	27	4173	7.38	0.97	13	1.99
93-03	190	200	17467	0.589	3.1	2.25	1	10	490	0.4	17	1.71	0.1	27	5821	5.69	0.97	14	1.77
93-03	200	210	17468	0.353	1.8	2.34	1	9	953	0.5	19	1.43	0.1	27	3452	6.30	0.97	13	1.90
93-03	210	220	17469	0.293	1.9	1.54	8	6	326	0.4	8	1.60	0.1	14	2883	3.22	0.45	9	0.83
93-03	220	230	17470	0.137	1.7	1.39	16	6	310	0.4	7	1.41	0.1	7	1328	2.05	0.15	8	0.61
93-03	230	240	17471	0.199	1.8	1.36	18	6	186	0.4	5	1.88	0.1	6	1960	1.72	0.24	8	0.65
93-03	240	250	17472	0.336	3.2	1.22	17	6	146	0.4	8	1.63	0.1	6	3284	1.75	0.23	8	0.61
93-03	250	260	17473	0.448	2.9	1.50	14	7	300	0.4	7	1.68	0.1	8	4293	2.04	0.32	8	0.67
93-03	260	270	17474	0.198	1.8	1.47	21	7	227	0.5	6	1.66	0.1	7	1735	1.77	0.31	7	0.66
93-03	270	280	17475	0.334	1.8	1.16	11	4	626	0.5	7	1.51	0.1	49	3231	1.56	0.19	9	0.86
93-03	280	290	17476	0.197	1.3	0.79	13	2	115	0.4	4	1.57	0.1	5	1646	1.00	0.17	6	0.49
93-03	290	300	17477	0.478	2.7	1.11	12	3	59	0.4	8	1.16	0.1	10	4334	1.77	0.12	10	0.81
93-03	300	310	17478	0.860	5.0	1.23	12	5	259	0.5	6	1.93	0.1	12	7819	2.00	0.22	8	0.68
93-03	310	320	17479	0.676	3.5	1.34	14	4	62	0.4	8	1.50	0.1	8	5983	1.69	0.16	9	0.82
93-03	320	330	17480	1.155	6.1	1.66	9	7	57	0.5	17	1.68	0.1	15	10000	2.53	0.13	10	0.94
93-03	330	340	17481	0.671	3.9	1.53	6	5	67	0.4	10	1.65	0.1	11	5910	2.09	0.10	9	0.76
93-03	340	350	17482	0.718	4.0	1.60	1	5	126	0.3	15	1.39	0.1	16	6236	3.08	0.39	11	1.33
93-03	350	360	17483	0.718	3.3	2.30	1	9	198	0.4	17	2.02	0.1	20	6395	5.47	0.57	10	1.44
93-03	360	370	17484	0.340	2.5	2.41	1	8	252	0.4	14	1.83	0.1	17	2919	4.25	0.72	12	1.91
93-03	370	380	17485	0.280	2.0	1.76	6	6	163	0.4	8	1.45	0.1	11	2601	2.92	0.43	11	1.19
93-03	380	390	17486	0.363	2.4	1.69	6	6	251	0.5	11	1.45	0.1	12	3317	2.97	0.42	10	1.31
93-03	390	400	17487	0.130	1.8	1.99	3	7	918	0.3	11	1.35	0.1	14	1170	3.41	0.78	10	1.54
93-03	400	410	17488	0.113	1.4	1.62	2	6	619	0.3	9	1.24	0.1	12	979	2.85	0.59	12	1.33

802-II

MIN-EN LABORATORIES
 705 W. 15th St.
 North Vancouver, B.C. Huckleberry

I.C.P. and Copper assay

New Canamin Resources

Phone: 980-8414

602-11

HOLE#	INTERVAL(feet)		SAMPLE	MN	MO	NA	NI	P	PB	SB	SR	TH	TI	TR	SN	W	CR		
	START	END	NAME	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM		
93-03	30	40	17451	950	26	0.03	1	360	19	6	29	2	599	120.0	41	6	2	6	48
93-03	40	50	17452	758	48	0.11	1	660	21	7	33	4	1268	189.9	51	9	2	9	57
93-03	50	60	17453	689	181	0.02	2	660	13	7	31	2	582	75.6	34	7	2	6	56
93-03	60	70	17454	391	87	0.03	1	820	14	9	17	4	1027	76.0	47	6	1	7	63
93-03	70	80	17455	355	63	0.04	1	970	13	7	13	4	577	76.5	41	5	1	7	94
93-03	80	90	17456	408	60	0.05	1	990	12	7	13	4	817	74.4	41	7	1	7	81
93-03	90	100	17457	423	222	0.06	1	1070	16	8	18	5	1452	82.0	51	7	2	10	123
93-03	100	110	17458	322	150	0.06	1	1050	16	9	16	4	1543	76.1	48	8	2	8	83
93-03	110	120	17459	690	14	0.18	20	680	13	9	37	4	2424	226.8	53	9	4	16	215
93-03	120	130	17460	509	180	0.11	6	930	16	12	27	5	1929	106.5	45	8	2	10	100
93-03	130	140	17461	378	105	0.03	1	990	10	5	11	5	1261	61.1	45	7	1	7	65
93-03	140	150	17462	396	125	0.05	1	1010	12	10	10	5	1420	56.0	47	7	2	7	69
93-03	150	160	17463	397	95	0.05	1	1090	14	5	7	4	2265	58.2	49	7	1	7	82
93-03	160	170	17464	331	107	0.05	1	1030	14	7	10	4	1353	55.5	44	6	1	6	72
93-03	170	180	17465	365	48	0.12	1	580	13	5	32	4	3092	127.5	48	9	2	8	77
93-03	180	190	17466	582	28	0.06	1	730	11	7	17	4	3397	241.8	49	9	2	11	69
93-03	190	200	17467	407	234	0.06	2	760	13	11	18	4	2552	224.9	48	9	2	11	88
93-03	200	210	17468	430	68	0.06	2	640	16	8	16	4	3196	260.5	55	9	2	12	72
93-03	210	220	17469	347	77	0.08	1	300	13	6	18	5	1000	70.2	36	6	1	10	145
93-03	220	230	17470	315	53	0.10	1	310	11	5	33	5	854	31.2	33	5	1	6	101
93-03	230	240	17471	331	165	0.07	4	420	14	6	16	5	270	28.8	34	5	1	8	142
93-03	240	250	17472	305	125	0.06	3	360	16	8	17	4	279	27.3	34	5	1	7	117
93-03	250	260	17473	443	235	0.08	5	400	30	10	20	5	296	26.7	55	5	1	8	122
93-03	260	270	17474	435	249	0.06	2	290	16	8	16	5	319	26.3	36	5	1	6	105
93-03	270	280	17475	314	151	0.05	419	350	18	22	22	7	167	33.5	827	1	1	164	81
93-03	280	290	17476	229	172	0.03	7	270	10	5	12	3	78	18.9	31	3	1	6	65
93-03	290	300	17477	233	98	0.06	7	390	15	8	14	3	803	32.9	45	5	1	8	91
93-03	300	310	17478	278	342	0.04	8	490	21	15	18	4	210	22.5	39	4	1	6	69
93-03	310	320	17479	230	173	0.04	9	450	20	12	19	4	226	32.0	82	5	1	5	67
93-03	320	330	17480	273	290	0.05	13	650	26	19	28	4	869	49.0	55	6	2	8	75
93-03	330	340	17481	252	216	0.06	6	420	19	12	61	3	925	53.4	38	5	2	6	62
93-03	340	350	17482	281	47	0.07	8	500	17	11	25	4	1802	103.0	52	7	2	10	118
93-03	350	360	17483	347	34	0.15	2	680	20	12	56	4	2726	225.1	57	10	3	13	121
93-03	360	370	17484	418	53	0.09	19	480	15	8	36	4	2194	128.3	46	8	3	10	117
93-03	370	380	17485	316	53	0.08	3	510	13	7	30	4	977	74.5	41	6	1	7	79
93-03	380	390	17486	309	63	0.08	4	530	16	8	27	4	1084	74.7	45	6	2	8	99
93-03	390	400	17487	350	83	0.09	3	520	13	5	23	4	1810	88.3	41	7	2	7	65
93-03	400	410	17488	399	31	0.07	2	450	13	4	42	4	1310	74.8	36	7	2	6	69

MIN-EN LABORATORIES
 705 W. 15th St.
 North Vancouver, B.C. Huckleberry
 Phone: 980-5814

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)	SAMPLE	Cu-ASSAY	AG	AL	AS	B	BA	BE	BI	CA	CD	CO	CU	FE	K	LI	MG	
HOLE#	START	END	NAME	%	PPM	%	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	%	%	PPM	%	
93-03	410	420	17489	0.091	1.3	2.04	1	7	439	0.3	10	1.72	0.1	13	877	2.95	0.79	13	1.59
93-03	420	430	17490	0.213	1.9	2.08	1	8	415	0.4	13	1.28	0.1	18	2047	4.47	0.99	15	1.73
93-03	430	440	17491	0.368	1.6	2.16	1	8	392	0.5	16	1.12	0.1	23	3291	6.34	1.06	12	2.22
93-03	440	450	17492	0.355	2.3	1.78	1	8	267	0.5	10	2.20	0.1	14	3264	3.47	0.50	7	1.15
93-03	450	460	17493	0.203	1.6	0.90	12	4	85	0.3	5	1.80	0.1	6	1825	0.94	0.20	6	0.51
93-03	460	470	17494	0.582	3.8	1.76	3	7	257	0.4	13	1.42	0.1	16	5390	2.57	0.37	13	1.39
93-03	470	480	17495	0.703	3.5	1.29	3	6	126	0.4	11	1.38	0.1	14	6057	2.80	0.22	11	0.98
93-03	480	490	17496	0.701	4.1	1.28	1	6	176	0.4	16	1.07	0.1	19	6594	3.04	0.28	10	1.04
93-03	490	500	17497	0.248	2.4	2.18	4	10	276	0.3	14	1.47	0.1	15	2568	3.03	0.48	12	1.42
93-03	500	510	17498	0.101	1.8	1.91	1	11	324	0.4	13	1.11	0.1	14	1085	3.15	0.69	14	1.55
93-03	510	520	17499	0.107	1.9	2.05	4	13	348	0.2	14	1.28	0.1	14	1050	3.04	0.59	12	1.52
93-03	520	530	17500	0.187	2.3	1.98	1	9	409	0.3	14	1.42	0.1	16	1825	2.92	0.64	13	1.57

II-21C

MIN-EN LABORATORIES
 705 W. 15th St.
 North Vancouver, B.C. Huckleberry
 Phone: 980-5814

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)		SAMPLE	MN	MO	NA	NI	P	PB	SB	SR	TH	TI	ZN	GA	SN	W	CR	
HOLE#	START	END	NAME	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	
93-03	410	420	17489	362	22	0.08	2	360	14	4	36	4	1713	110.2	36	8	2	6	58
93-03	420	430	17490	516	46	0.06	1	540	10	6	34	4	2199	122.9	46	8	2	7	56
93-03	430	440	17491	524	20	0.06	1	550	16	7	21	4	2651	241.4	57	10	2	10	60
93-03	440	450	17492	454	83	0.06	1	460	14	9	44	5	1054	139.1	37	7	1	7	63
93-03	450	460	17493	198	60	0.04	4	330	19	5	34	3	46	21.2	27	4	1	4	58
93-03	460	470	17494	302	63	0.07	5	720	19	11	102	4	1500	87.4	50	7	2	7	58
93-03	470	480	17495	284	114	0.06	5	570	18	12	51	4	739	67.2	46	6	1	6	67
93-03	480	490	17496	267	74	0.08	4	490	19	12	41	4	1573	76.5	47	7	1	8	88
93-03	490	500	17497	325	140	0.14	2	480	17	8	94	4	1957	90.0	41	8	2	7	68
93-03	500	510	17498	344	122	0.13	1	420	12	4	55	4	2298	93.4	39	8	2	7	72
93-03	510	520	17499	298	34	0.14	1	410	13	5	64	4	2464	102.2	36	8	2	8	74
93-03	520	530	17500	273	73	0.12	1	410	13	5	128	3	2329	96.3	36	8	2	7	77

112-II

MIN-EN LABORATORIES

705 W. 15th St.

North Vancouver, B.C.

Phone: 980-5814

Huckleberry

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)	SAMPLE NAME	Cu-ASSAY %	AG PPM	AL %	AS PPM	B PPM	BA PPM	BE PPM	BI PPM	CA %	CD PPM	CO PPM	CU PPM	FE %	K %	LI PPM	MG %	
93-04	30	40	18501	0.486	2.4	1.28	1	5	154	0.1	1	1.18	0.1	23	4121	6.19	0.50	7	1.31
93-04	40	50	18502	0.320	1.8	1.88	1	5	223	0.3	4	1.29	0.1	24	2927	6.09	0.75	9	1.94
93-04	50	60	18503	0.611	3.4	2.18	1	8	290	0.3	1	1.53	0.1	34	5355	5.95	0.69	9	1.74
93-04	60	70	18504	1.960	10.2	3.91	1	12	281	0.3	1	2.47	0.1	36	10000	6.79	0.78	14	2.81
93-04	70	80	18505	0.290	2.5	4.05	1	14	178	0.5	7	2.51	0.1	24	3026	5.38	0.54	11	2.20
93-04	80	90	18506	0.217	2.2	5.16	1	17	369	0.6	9	2.84	0.1	23	2161	5.12	1.00	12	3.01
93-04	90	100	18507	0.855	5.7	1.83	1	8	237	0.2	1	1.57	0.1	29	7734	5.48	0.52	10	1.21
93-04	100	110	18508	0.529	4.4	1.09	1	8	128	0.2	6	1.61	0.1	22	4718	5.67	0.28	8	0.92
93-04	110	120	18509	0.401	3.4	3.93	1	18	346	0.4	10	2.14	0.1	26	3761	5.55	0.79	10	2.34
93-04	120	130	18510	0.597	4.4	2.97	1	14	296	0.3	5	1.37	0.1	25	5078	4.51	0.91	15	3.02
93-04	130	140	18511	1.235	8.7	4.51	1	17	367	0.4	1	2.32	0.1	26	10000	4.21	1.30	17	3.27
93-04	140	150	18512	0.176	1.7	0.84	6	8	82	0.3	1	1.48	0.1	6	1543	1.03	0.18	7	0.63
93-04	150	160	18513	0.095	1.2	0.92	1	7	109	0.3	2	1.30	0.1	8	922	1.29	0.20	8	0.66
93-04	160	170	18514	0.119	1.2	0.85	1	6	84	0.2	3	1.10	0.1	8	1125	1.40	0.17	8	0.62
93-04	170	180	18515	0.396	2.5	0.81	1	10	68	0.3	1	1.09	0.1	9	3589	1.67	0.15	8	0.65
93-04	180	190	18516	0.134	1.5	0.84	7	9	82	0.2	3	0.98	0.1	9	1253	1.61	0.16	8	0.69
93-04	190	200	18517	0.111	1.3	0.71	2	6	60	0.2	1	1.03	0.1	6	1110	1.19	0.12	8	0.62
93-04	200	210	18518	0.083	1.0	0.67	1	7	45	0.3	3	0.88	0.1	6	795	1.03	0.12	7	0.58
93-04	210	220	18519	0.046	0.9	0.66	1	5	33	0.2	3	1.51	0.1	5	458	0.94	0.09	8	0.58
93-04	220	230	18520	0.143	1.6	0.75	3	6	58	0.2	1	1.61	0.1	6	1363	1.16	0.12	8	0.58
93-04	230	240	18521	0.214	2.0	0.85	4	6	74	0.3	2	1.64	0.1	8	2057	1.63	0.10	8	0.57
93-04	240	250	18522	0.176	2.3	0.94	1	7	123	0.2	3	1.55	0.1	10	1710	1.89	0.20	9	0.72
93-04	250	260	18523	0.453	4.3	4.10	1	15	431	0.4	4	2.85	0.1	25	4599	4.08	1.59	20	3.01
93-04	260	270	18524	0.165	1.9	1.27	1	4	212	0.3	1	1.80	0.1	8	1667	1.79	0.38	9	0.74
93-04	270	280	18525	0.479	3.2	2.36	1	7	549	0.3	9	1.39	0.1	22	4007	4.35	1.07	15	2.05
93-04	280	290	18526	0.368	0.2	2.47	1	9	170	0.5	9	1.47	0.1	26	3280	8.32	0.58	10	1.68
93-04	290	300	18527	0.478	1.1	2.91	1	8	124	0.6	5	1.67	0.1	25	4506	7.51	0.47	9	1.73
93-04	300	310	18528	0.310	1.3	2.60	1	8	77	0.2	7	1.69	0.1	23	2893	6.77	0.30	8	1.06
93-04	310	320	18529	0.841	3.6	2.62	1	6	97	0.3	1	1.67	0.1	27	7400	6.38	0.41	10	1.26
93-04	320	330	18530	1.180	6.3	3.50	1	10	179	0.3	1	2.08	0.1	27	10000	6.79	0.51	11	1.38
93-04	330	340	18531	0.296	1.5	3.49	1	10	143	0.3	10	2.06	0.1	24	2854	6.61	0.37	10	1.30
93-04	340	350	18532	0.510	1.8	2.40	1	6	104	0.1	4	1.63	0.1	24	4395	6.60	0.42	9	1.30
93-04	350	360	18533	0.708	4.3	3.61	1	11	307	0.4	10	1.69	0.1	34	6718	7.75	0.83	13	1.98
93-04	360	370	18534	0.759	4.7	3.63	1	11	449	0.3	6	1.36	0.1	39	7676	7.40	1.37	17	2.47
93-04	370	380	18535	0.335	2.4	4.78	1	14	442	0.2	13	1.67	0.1	29	3435	5.92	1.64	18	3.37
93-04	380	390	18536	0.310	2.4	1.58	1	5	206	0.4	6	1.30	0.1	19	3076	4.02	0.46	9	1.04
93-04	390	395	18537	0.129	1.6	2.02	1	6	236	0.4	7	1.56	0.1	18	1166	3.59	0.61	11	1.18

11-212

MIN-EN LABORATORIES
 705 W. 15th St.
 North Vancouver, B.C.Huckleberry
 Phone: 980-6014

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)		SAMPLE	MN	MO	NA	NI	P	PB	SB	SR	TH	TI	V	ZN	GA	SN	W	CR
HOLE#	START	END	NAME	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM
93-04	30	40	18501	315	15	0.08	1	700	10	7	12	5	1972	209.3	44	7	4	8	79
93-04	40	50	18502	353	10	0.14	14	720	5	5	25	6	2351	230.0	40	10	4	11	162
93-04	50	60	18503	340	34	0.16	18	670	10	8	34	6	2603	233.8	46	9	3	11	136
93-04	60	70	18504	409	49	0.18	46	750	25	28	106	8	2318	247.8	88	11	5	18	250
93-04	70	80	18505	507	4	0.44	21	670	13	8	82	9	2245	238.0	35	11	5	14	189
93-04	80	90	18506	491	24	0.50	21	630	8	6	94	9	2606	250.7	38	12	4	16	219
93-04	90	100	18507	306	24	0.10	16	1020	10	11	40	3	3081	80.1	57	9	4	6	65
93-04	100	110	18508	315	9	0.06	5	920	15	7	20	5	2933	76.3	46	7	5	6	69
93-04	110	120	18509	416	15	0.37	52	870	12	7	133	9	2617	188.7	42	11	4	17	271
93-04	120	130	18510	346	27	0.15	29	870	12	8	81	6	2941	157.8	54	9	4	14	239
93-04	130	140	18511	467	100	0.44	24	610	20	16	118	9	2356	219.0	64	11	3	13	188
93-04	140	150	18512	196	34	0.05	6	260	9	4	22	4	145	17.6	27	3	1	5	95
93-04	150	160	18513	224	28	0.06	4	290	9	3	28	4	377	20.6	29	3	1	3	63
93-04	160	170	18514	179	31	0.06	2	290	10	3	32	3	533	23.6	28	3	1	4	85
93-04	170	180	18515	195	15	0.05	6	350	10	6	18	4	379	24.1	36	3	1	4	70
93-04	180	190	18516	202	48	0.06	3	350	6	3	17	4	947	31.7	30	4	1	5	85
93-04	190	200	18517	177	74	0.04	3	270	8	3	9	3	378	24.0	32	3	1	3	63
93-04	200	210	18518	168	46	0.06	3	230	10	2	9	3	544	20.4	27	3	1	4	90
93-04	210	220	18519	161	27	0.05	1	210	11	1	13	4	563	22.1	26	3	1	4	80
93-04	220	230	18520	182	60	0.05	6	230	8	3	18	3	449	21.6	28	3	1	4	95
93-04	230	240	18521	214	57	0.09	5	280	13	4	28	4	839	24.4	34	3	1	5	110
93-04	240	250	18522	252	50	0.08	2	270	12	3	23	4	1008	31.8	32	4	2	4	81
93-04	250	260	18523	483	119	0.31	11	650	13	8	71	7	2922	234.0	40	12	5	11	104
93-04	260	270	18524	366	60	0.15	6	270	11	3	36	4	664	31.4	30	4	1	5	118
93-04	270	280	18525	303	135	0.11	4	510	11	7	40	9	2837	198.2	42	10	4	11	104
93-04	280	290	18526	377	58	0.21	1	620	12	8	105	10	2460	476.5	47	12	5	16	97
93-04	290	300	18527	377	19	0.20	1	650	16	8	97	4	2221	439.6	55	11	4	14	90
93-04	300	310	18528	351	25	0.27	1	540	13	5	115	3	2268	325.3	36	9	4	11	83
93-04	310	320	18529	387	8	0.25	4	570	11	10	130	4	2186	272.2	42	9	3	9	72
93-04	320	330	18530	469	95	0.22	7	600	18	16	140	4	2851	294.4	51	10	5	12	80
93-04	330	340	18531	504	34	0.28	1	550	13	6	111	4	3162	316.8	45	10	4	11	86
93-04	340	350	18532	457	29	0.22	1	500	10	6	58	3	2730	296.4	44	9	4	11	88
93-04	350	360	18533	473	63	0.20	2	570	14	11	93	4	3956	393.1	59	12	4	14	99
93-04	360	370	18534	426	98	0.17	10	670	9	12	85	4	3695	330.2	65	12	5	16	185
93-04	370	380	18535	450	109	0.38	19	620	2	6	78	4	3862	322.7	45	12	5	16	228
93-04	380	390	18536	468	20	0.09	4	270	12	6	22	3	1587	84.7	46	6	2	6	93
93-04	390	395	18537	444	32	0.10	4	300	22	3	33	4	1357	104.8	38	6	1	5	73

812-213

MIN-EN LABORATORIES
 705 W. 15th St.
 North Vancouver, B.C. Huckleberry
 Phone: 980-5814

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)	SAMPLE	Cu-ASSAY	AG	AL	AS	B	BA	BE	BI	CA	CD	CO	CU	FE	K	LI	MG	
HOLE#	START	END	NAME	%	PPM	%	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	%	%	PPM	%	
93-05	70	80	18201	0.332	0.9	3.90	1	11	349	0.7	16	2.11	0.1	23	3173	6.10	0.70	11	1.63
93-05	80	90	18202	0.247	0.1	2.83	1	8	113	0.7	12	1.58	0.1	21	2427	7.94	0.44	7	1.24
93-05	90	100	18203	0.616	0.8	2.79	1	8	101	0.4	17	1.77	0.1	26	5668	8.15	0.42	7	1.23
93-05	100	110	18204	0.483	1.9	3.07	1	9	364	0.3	18	1.56	0.1	27	4825	6.45	1.03	13	2.30
93-05	110	120	18205	0.337	0.1	1.79	1	5	137	0.4	18	1.46	0.1	25	3230	8.39	0.45	7	1.29
93-05	120	130	18206	0.795	3.5	2.73	1	8	259	0.4	21	1.75	0.1	31	8088	8.35	0.80	12	2.01
93-05	130	140	18207	0.384	0.6	2.81	1	8	365	0.4	18	1.65	0.1	27	3708	7.72	0.77	10	1.87
93-05	140	150	18208	0.253	0.3	2.61	1	7	294	0.5	15	1.54	0.1	24	2508	6.49	0.76	11	2.02
93-05	150	160	18209	0.282	0.3	2.34	1	7	285	0.6	15	1.43	0.1	23	2626	6.95	0.76	10	1.84
93-05	160	170	18210	0.535	4.4	2.46	1	7	345	0.5	14	1.76	0.1	20	5564	4.30	0.71	12	1.36
93-05	170	180	18211	0.212	1.8	1.47	2	3	178	0.4	9	1.37	0.1	12	2050	2.49	0.40	11	1.06
93-05	180	190	18212	0.204	2.1	2.57	1	8	462	0.5	14	1.74	0.1	25	2093	4.74	0.76	11	1.21
93-05	190	200	18213	0.161	1.7	4.17	1	13	449	0.6	15	1.91	0.1	23	1684	5.38	1.17	14	2.37
93-05	200	210	18214	0.152	1.8	2.82	1	9	446	0.5	14	1.84	0.1	17	1500	4.11	0.44	8	0.86
93-05	210	220	18215	0.293	2.3	2.69	1	8	555	0.4	16	1.75	0.1	20	2786	4.32	0.80	11	1.51
93-05	220	230	18216	0.230	2.3	3.69	8	12	1003	0.8	17	2.28	0.1	22	2231	5.74	1.12	16	2.56
93-05	230	240	18217	0.160	4.3	3.83	39	13	547	0.8	11	3.46	0.1	17	1599	4.76	0.48	14	1.19
93-05	240	250	18218	0.204	1.9	4.38	14	14	1422	0.8	15	2.28	0.1	23	1983	5.57	0.93	15	2.63
93-05	250	260	18219	0.278	2.0	4.07	12	13	955	0.7	16	2.67	0.1	22	2721	5.00	0.92	12	2.75
93-05	260	270	18220	0.170	2.5	4.15	5	14	632	0.8	15	2.50	0.1	19	1576	5.19	0.49	7	1.37
93-05	270	280	18221	0.259	2.6	3.06	1	10	932	0.5	17	1.62	0.1	21	2546	4.85	1.08	13	1.82
93-05	280	290	18222	0.312	2.7	3.07	2	10	936	0.4	17	1.63	0.1	21	2502	4.87	1.05	12	1.81
93-05	290	300	18223	0.311	2.8	2.78	1	9	961	0.5	16	1.64	0.1	21	2944	4.64	0.99	13	1.60
93-05	300	310	18224	0.248	2.1	5.14	16	17	516	0.7	16	2.55	0.1	20	2474	5.03	0.78	14	2.20
93-05	310	320	18225	0.429	2.9	5.21	14	16	429	0.7	17	2.84	0.1	22	4194	5.06	0.82	16	2.68
93-05	320	330	18226	0.220	2.4	3.91	5	11	577	0.6	15	1.87	0.1	22	2074	4.96	1.02	13	1.78
93-05	330	340	18227	0.233	2.1	3.12	1	9	598	0.5	13	1.65	0.1	19	2222	4.50	0.83	12	1.52
93-05	340	350	18228	0.202	1.9	2.72	1	8	884	0.6	17	1.21	0.1	22	1895	5.58	1.11	14	1.85
93-05	350	360	18229	0.530	3.8	3.74	1	11	950	0.6	22	1.59	0.1	26	4966	5.45	1.36	18	2.23
93-05	360	370	18230	0.335	2.9	3.35	5	12	559	0.6	15	2.29	0.1	18	3215	4.02	0.81	14	1.50
93-05	370	380	18231	0.380	3.1	3.04	6	11	604	0.7	16	2.01	0.1	20	3663	4.42	0.89	12	1.56
93-05	380	390	18232	0.322	3.1	3.09	3	10	618	0.4	16	1.55	0.1	19	3113	4.04	1.01	13	1.63
93-05	390	400	18233	0.263	2.3	2.82	3	8	747	0.4	14	1.45	0.1	16	2430	3.54	0.86	14	1.49
93-05	400	410	18234	0.329	2.6	3.11	1	10	467	0.6	17	1.43	0.1	23	3142	4.83	0.93	14	1.60
93-05	410	420	18235	0.330	3.2	4.34	14	13	1538	0.7	18	2.21	0.1	21	3125	5.18	0.99	11	1.63
93-05	420	430	18236	0.199	2.3	2.61	1	8	679	0.4	18	1.29	0.1	21	1935	4.87	1.06	14	1.71
93-05	430	440	18237	0.301	2.7	2.73	1	9	434	0.5	17	1.42	0.1	21	3006	4.69	0.92	13	1.64
93-05	440	450	18238	0.242	2.4	2.92	1	10	831	0.5	17	1.63	0.1	18	2256	4.52	0.85	10	1.56

612-77

MIN-EN LABORATORIES

705 W. 15th St.

North Vancouver, B.C.

Phone: 980-5814

Huckleberry

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)		SAMPLE	MN	MO	NA	NI	P	PB	SB	SR	TH	TI	V	ZN	GA	SN	W	CR
HOLE#	START	END	NAME	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM
93-05	70	80	18201	413	22	0.21	1	540	16	10	308	5	2897	324.9	51	11	4	14	81
93-05	80	90	18202	383	55	0.39	1	640	12	6	201	3	2563	478.3	41	11	3	15	82
93-05	90	100	18203	417	30	0.28	1	680	18	11	281	3	2847	476.8	50	11	3	16	86
93-05	100	110	18204	431	15	0.21	1	720	16	8	128	4	3581	354.7	50	11	3	12	52
93-05	110	120	18205	573	51	0.13	1	590	12	6	63	3	3616	477.9	46	11	3	16	89
93-05	120	130	18206	804	10	0.15	1	700	17	13	114	3	3799	478.1	62	11	3	16	80
93-05	130	140	18207	544	11	0.24	1	590	13	8	92	3	3690	460.0	57	12	4	16	86
93-05	140	150	18208	527	31	0.24	9	680	10	6	59	4	2861	348.2	53	10	3	16	160
93-05	150	160	18209	610	19	0.20	7	680	14	5	33	4	2757	360.3	43	10	3	14	123
93-05	160	170	18210	411	56	0.10	2	810	15	11	42	4	2041	117.3	44	7	3	8	66
93-05	170	180	18211	277	52	0.05	2	1030	10	5	18	3	1215	62.9	30	6	2	5	59
93-05	180	190	18212	530	74	0.15	1	810	9	6	44	4	2096	97.0	37	7	2	7	66
93-05	190	200	18213	537	44	0.30	12	540	14	9	61	5	2755	186.2	41	11	4	13	131
93-05	200	210	18214	388	70	0.31	2	310	10	6	71	3	2190	98.6	37	7	3	10	108
93-05	210	220	18215	407	67	0.18	6	340	14	9	80	4	2230	138.9	38	8	2	9	76
93-05	220	230	18216	654	49	0.25	17	620	12	8	94	4	2789	153.6	48	9	3	15	189
93-05	230	240	18217	875	42	0.36	12	860	37	87	110	5	1560	120.4	99	9	3	10	110
93-05	240	250	18218	765	46	0.41	25	870	25	10	99	5	2684	183.0	52	10	3	18	240
93-05	250	260	18219	606	41	0.37	28	890	16	10	103	5	2575	210.6	45	10	3	19	246
93-05	260	270	18220	522	113	0.38	1	950	14	10	101	5	2536	131.3	43	10	3	10	81
93-05	270	280	18221	348	156	0.27	1	1010	12	8	67	5	3057	120.3	36	9	3	8	65
93-05	280	290	18222	353	150	0.26	1	990	8	7	67	4	3115	119.9	36	9	3	8	67
93-05	290	300	18223	355	83	0.11	1	710	9	7	45	4	3006	119.7	40	9	3	8	65
93-05	300	310	18224	618	28	0.44	8	810	15	14	131	6	2564	173.8	39	11	5	14	125
93-05	310	320	18225	668	52	0.34	11	820	21	14	124	4	2771	203.0	47	11	5	16	154
93-05	320	330	18226	397	43	0.40	1	960	9	7	86	4	3077	119.5	32	9	3	9	69
93-05	330	340	18227	349	59	0.23	3	840	12	7	121	4	2526	122.8	36	8	3	8	63
93-05	340	350	18228	396	55	0.13	1	980	11	6	46	4	3242	138.7	37	9	2	8	57
93-05	350	360	18229	394	42	0.25	5	910	19	12	105	4	3901	173.9	45	10	3	11	60
93-05	360	370	18230	375	136	0.18	2	900	16	10	92	5	2177	112.2	35	9	2	7	44
93-05	370	380	18231	319	248	0.10	5	860	13	11	37	4	2328	107.2	36	9	3	7	45
93-05	380	390	18232	320	247	0.29	2	900	10	7	90	4	3024	107.3	32	9	3	7	55
93-05	390	400	18233	298	87	0.27	2	930	8	6	75	4	2550	112.4	31	8	2	7	55
93-05	400	410	18234	407	99	0.17	1	680	12	8	70	4	3246	137.5	38	9	3	9	65
93-05	410	420	18235	441	40	0.33	1	950	16	11	109	4	3108	123.0	44	10	3	10	82
93-05	420	430	18236	456	146	0.19	1	820	11	5	65	3	3319	134.7	37	9	3	8	70
93-05	430	440	18237	461	32	0.19	4	960	11	7	78	4	3022	129.4	41	9	3	8	72
93-05	440	450	18238	465	171	0.29	1	960	13	6	118	3	3171	137.9	39	9	2	10	104

II-215

MIN-EN LABORATORIES
 705 W. 15th St.
 North Vancouver, B.C.
 Phone: 980-5814

Huckleberry

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)		SAMPLE	Cu-ASSAY	AG	AL	AS	B	BA	BE	BI	CA	CD	CO	CU	FE	K	LI	MG
HOLE#	START	END	NAME	%	PPM	%	PPM	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	%	%	PPM	%
93-05	450	460	18239	0.207	1.9	2.39	12	7	491	0.4	11	1.79	0.1	12	1994	2.59	0.73	11	1.29
93-05	460	470	18240	0.237	1.8	1.67	13	5	240	0.5	6	1.75	0.1	9	2411	1.96	0.59	10	0.91

712 - II

MIN-EN LABORATORIES
705 W. 15th St.
North Vancouver, B.C.
Phone: 980-5814

Huckleberry

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)		SAMPLE	MN	MO	NA	NI	P	PB	SB	SR	TH	TI	V	ZN	GA	SN	W	CR
HOLE#	START	END	NAME	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM
93-05	450	460	18239	379	56	0.16	8	740	13	6	52	3	1423	76.7	29	7	1	8	100
93-05	460	470	18240	405	145	0.07	7	850	13	5	15	3	673	47.2	27	5	1	7	120

412-II

MIN-EN LABORATORIES
 705 W. 15th St.
 North Vancouver, B.C. Huckleberry

I.C.P. and Copper assay

New Canamin Resources

Phone: 980-5014

HOLE#	INTERVAL(feet)	SAMPLE	Cu-ASSAY	AG	AL	AS	B	BA	BE	BI	CA	CD	CO	CU	FE	K	LI	MG	
HOLE#	START	END	NAME	%	PPM	%	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	%	%	PPM	%	
93-06	70	80	18601	0.157	0.1	2.26	1	10	170	0.5	8	2.08	0.1	18	1454	6.00	0.28	7	1.14
93-06	80	90	18602	0.432	0.1	2.53	1	12	165	0.6	12	2.01	0.1	19	3760	6.70	0.34	7	1.19
93-06	90	100	18603	0.605	1.8	2.48	1	12	339	0.3	15	2.94	0.1	20	4833	5.82	0.69	10	1.64
93-06	100	110	18604	0.216	0.3	3.86	1	17	583	0.3	21	1.20	0.1	29	2242	8.92	1.62	15	2.94
93-06	110	120	18605	0.517	1.1	2.04	1	11	374	0.3	18	2.60	0.1	24	4336	7.07	0.97	8	2.01
93-06	120	130	18606	0.828	3.0	2.09	1	12	276	0.5	20	3.15	0.1	26	7026	9.09	0.93	11	2.06
93-06	130	140	18607	1.496	4.9	1.91	1	11	202	0.1	22	2.58	0.1	24	10000	7.74	0.94	11	2.07
93-06	140	150	18608	1.465	9.0	2.94	1	14	269	0.3	24	2.53	0.1	24	10000	6.67	0.99	11	2.24
93-06	150	160	18609	0.490	2.0	4.04	1	17	320	0.4	16	3.13	0.1	22	4587	6.60	1.18	13	2.78
93-06	160	170	18610	0.712	2.7	2.43	1	12	294	0.3	18	3.41	0.1	24	6605	6.44	1.15	13	2.56
93-06	170	180	18611	0.770	1.6	2.23	1	12	304	0.2	23	2.83	0.1	26	6947	7.14	1.19	12	2.50
93-06	180	190	18612	0.828	2.1	2.19	1	12	326	0.3	20	2.22	0.1	25	7788	6.99	1.09	12	2.27
93-06	190	200	18613	0.625	2.3	3.15	1	16	380	0.5	18	3.08	0.1	25	5581	6.24	1.02	14	2.40
93-06	200	210	18614	0.332	2.9	2.92	1	15	516	0.5	13	3.18	0.1	15	3052	4.28	0.76	13	1.69
93-06	210	220	18615	0.187	1.8	2.91	1	14	328	0.5	12	2.77	0.1	13	1805	3.51	0.63	16	1.52
93-06	220	230	18616	0.386	2.3	2.34	10	12	588	0.6	12	2.55	0.1	16	3407	3.11	0.80	15	1.72
93-06	230	240	18617	0.227	1.6	1.89	4	10	341	0.4	7	1.72	0.1	10	2087	2.48	0.44	13	1.20
93-06	240	250	18618	0.369	1.9	1.23	1	9	422	0.5	8	1.39	0.1	11	3382	2.61	0.35	10	0.75
93-06	250	260	18619	0.302	2.1	2.06	1	11	540	0.4	14	1.19	0.1	15	2837	4.07	0.49	11	0.96
93-06	260	270	18620	0.329	3.4	3.43	1	16	1249	0.2	21	1.80	0.1	21	3293	4.85	0.92	12	1.68
93-06	270	280	18621	0.558	3.8	2.17	1	12	417	0.3	20	1.36	0.1	21	5005	4.44	0.72	11	1.67
93-06	280	290	18622	0.421	3.0	2.10	1	12	598	0.3	15	1.40	0.1	22	4067	4.22	0.69	12	1.47
93-06	290	300	18623	0.163	1.7	1.67	5	11	213	0.3	8	1.41	0.1	10	1620	2.54	0.39	12	1.14
93-06	300	310	18624	0.092	1.3	1.45	7	8	149	0.3	6	1.27	0.1	7	1023	1.93	0.31	11	0.83
93-06	310	320	18625	0.128	1.1	1.07	1	5	61	0.4	4	1.38	0.1	6	1215	1.88	0.23	10	0.73
93-06	320	330	18626	0.112	1.1	1.19	5	5	93	0.4	5	1.37	0.1	5	1043	1.77	0.17	7	0.53
93-06	330	340	18627	0.111	1.2	1.18	5	5	71	0.3	6	1.63	0.1	6	1097	1.85	0.18	9	0.67
93-06	340	350	18628	0.078	1.1	1.14	3	6	66	0.3	6	1.23	0.1	6	747	2.05	0.22	10	0.64
93-06	350	360	18629	0.171	1.1	1.14	1	7	75	0.4	8	1.06	0.1	10	1595	3.23	0.24	11	0.74
93-06	360	370	18630	0.400	2.4	1.30	1	7	47	0.3	8	1.23	0.1	9	3620	2.21	0.25	12	0.92
93-06	370	380	18631	0.398	2.3	2.19	1	9	310	0.3	13	1.22	0.1	18	3738	4.13	0.88	15	1.73
93-06	380	390	18632	0.303	2.4	2.81	12	12	154	0.4	9	2.35	0.1	11	2843	2.84	0.35	11	1.24
93-06	390	400	18633	0.304	1.8	1.27	2	7	46	0.3	7	1.50	0.1	7	2541	2.05	0.18	11	0.77
93-06	400	410	18634	0.193	1.3	1.26	1	7	81	0.5	8	1.05	0.1	9	1891	2.98	0.26	13	0.90
93-06	410	420	18635	0.384	2.5	1.91	1	8	190	0.4	12	1.95	0.1	15	3425	3.37	0.47	11	1.27
93-06	420	430	18636	0.460	3.2	2.67	1	11	221	0.3	12	2.66	0.1	15	3968	3.27	0.70	11	1.43
93-06	430	440	18637	0.382	2.9	2.92	1	12	205	0.4	15	1.81	0.1	25	3248	4.31	0.74	11	1.59
93-06	440	450	18638	0.291	2.6	3.51	1	14	193	0.4	13	2.39	0.1	18	2661	4.56	0.71	10	1.59

II-218

MIN-EN LABORATORIES
 705 W. 15th St.
 North Vancouver, B.C. Huckleberry
 Phone: 980-5814

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)		SAMPLE	MN	MO	NA	NI	P	PB	SB	SR	TH	TI	V	ZN	GA	SN	W	CR
HOLE#	START	END	NAME	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM
93-06	70	80	18601	368	10	0.13	1	700	18	6	93	5	1245	326.1	49	9	1	10	77
93-06	80	90	18602	359	36	0.17	1	670	16	10	150	5	1255	389.8	39	10	1	11	94
93-06	90	100	18603	335	24	0.12	5	610	18	11	101	3	2364	286.1	37	10	2	10	78
93-06	100	110	18604	360	40	0.35	1	650	16	8	49	5	4275	401.0	41	13	3	14	114
93-06	110	120	18605	376	41	0.13	2	600	21	10	57	4	2969	348.9	41	10	2	11	71
93-06	120	130	18606	766	17	0.09	1	640	32	14	50	3	2769	399.1	56	11	1	12	78
93-06	130	140	18607	468	43	0.08	1	720	29	22	53	3	2839	391.8	53	10	2	12	83
93-06	140	150	18608	391	66	0.31	12	800	28	23	65	4	2736	312.3	46	10	2	15	154
93-06	150	160	18609	423	46	0.42	15	660	19	14	91	4	2677	331.7	43	11	3	15	175
93-06	160	170	18610	409	74	0.16	13	640	23	13	78	3	2905	343.0	45	11	3	13	119
93-06	170	180	18611	383	101	0.12	5	690	24	14	67	3	3554	432.5	48	12	3	13	81
93-06	180	190	18612	419	226	0.14	4	590	23	13	50	4	3028	366.6	43	10	2	12	85
93-06	190	200	18613	1558	23	0.24	11	690	59	22	69	4	2538	341.3	95	10	2	13	117
93-06	200	210	18614	1193	86	0.13	11	780	32	15	77	4	1852	135.5	59	8	2	11	134
93-06	210	220	18615	772	112	0.16	3	790	17	8	78	4	1710	103.8	41	8	2	10	123
93-06	220	230	18616	833	92	0.05	5	890	17	10	44	4	1202	92.2	40	7	2	7	74
93-06	230	240	18617	486	150	0.08	3	840	21	6	35	4	819	73.5	41	6	1	6	82
93-06	240	250	18618	583	122	0.03	6	770	18	8	17	4	656	91.9	38	5	1	6	75
93-06	250	260	18619	608	71	0.12	6	780	19	8	41	4	2174	112.2	45	6	2	7	70
93-06	260	270	18620	455	175	0.26	1	870	13	10	78	5	3468	124.6	45	9	3	9	80
93-06	270	280	18621	398	108	0.07	3	980	15	11	40	4	2768	134.3	47	8	2	9	79
93-06	280	290	18622	409	129	0.09	3	920	20	9	34	5	2067	114.3	42	8	2	8	88
93-06	290	300	18623	403	261	0.05	3	680	16	6	19	5	1220	60.7	40	7	2	6	78
93-06	300	310	18624	393	122	0.08	1	500	12	4	18	4	1009	32.3	33	5	1	6	89
93-06	310	320	18625	340	161	0.07	2	640	12	4	19	3	401	35.9	30	4	1	4	57
93-06	320	330	18626	358	71	0.10	2	360	11	4	26	4	384	25.4	27	3	1	4	69
93-06	330	340	18627	405	88	0.06	1	290	10	4	19	3	546	31.2	32	4	1	5	77
93-06	340	350	18628	444	78	0.08	1	320	11	3	19	4	771	35.7	29	4	1	4	61
93-06	350	360	18629	433	169	0.04	1	190	12	5	11	4	913	89.9	33	5	1	5	72
93-06	360	370	18630	382	178	0.05	6	490	17	8	15	3	856	76.5	38	5	2	6	83
93-06	370	380	18631	352	89	0.07	3	520	13	8	33	4	2335	173.9	42	8	2	8	87
93-06	380	390	18632	344	104	0.15	4	970	19	9	71	5	1238	81.6	35	8	2	7	75
93-06	390	400	18633	334	260	0.05	4	550	16	6	20	4	532	66.1	30	5	1	6	96
93-06	400	410	18634	402	137	0.03	1	330	14	6	11	4	861	90.3	31	5	1	5	64
93-06	410	420	18635	286	63	0.06	3	460	17	9	45	5	1582	103.9	37	7	2	7	101
93-06	420	430	18636	278	94	0.16	1	730	17	9	70	4	1759	89.3	33	8	2	6	58
93-06	430	440	18637	415	42	0.24	1	880	21	8	74	4	2123	105.6	38	9	2	8	90
93-06	440	450	18638	378	63	0.29	1	890	17	9	74	4	2193	115.7	39	9	2	7	80

612-11

MIN-EN LABORATORIES
 705 W. 15th St.
 North Vancouver, B.C.
 Phone: 980-5814

Huckleberry

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)		SAMPLE	Cu-ASSAY	AG	AL	AS	B	BA	BE	BI	CA	CD	CO	CU	FE	K	LI	MG
HOLE#	START	END	NAME	%	PPM	%	PPM	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	%	%	PPM	%
93-06	450	460	18639	0.326	2.9	3.58	1	15	268	0.4	15	2.16	0.1	19	3219	4.53	0.77	12	1.65
93-06	460	470	18640	0.440	3.1	2.20	1	11	263	0.2	16	1.35	0.1	20	4129	4.66	0.84	12	1.64
93-06	470	480	18641	0.304	2.7	2.07	1	11	159	0.4	14	1.79	0.1	15	2939	3.87	0.56	12	1.38
93-06	480	490	18642	0.340	3.1	1.50	1	9	170	0.1	18	1.49	0.1	18	2973	4.51	0.58	10	1.32
93-06	490	500	18643	0.538	4.1	1.84	1	10	143	0.1	16	1.96	0.1	19	5148	4.45	0.62	12	1.36
93-06	500	510	18644	0.652	4.3	2.37	1	12	196	0.3	18	1.78	0.1	20	5728	4.67	0.64	10	1.40
93-06	510	520	18645	0.201	2.7	4.75	17	20	518	0.5	16	2.65	0.1	17	1879	4.31	0.72	11	1.57
93-06	520	530	18646	0.277	2.8	2.87	1	9	276	0.3	13	1.95	0.1	17	2788	3.76	0.58	12	1.35
93-06	530	540	18647	0.523	3.6	1.86	1	9	325	0.2	17	1.32	0.1	22	4632	4.93	0.83	11	1.55
93-06	540	550	18648	0.460	3.5	2.78	1	13	485	0.2	19	2.31	0.1	21	4103	5.03	0.77	9	1.50
93-06	550	560	18649	0.815	3.9	2.96	1	11	620	0.2	9	1.62	0.1	19	6870	4.08	0.93	13	1.51
93-06	560	570	18650	0.402	2.7	3.62	1	20	925	0.5	15	2.14	0.1	19	3426	4.95	0.89	14	1.70
93-06	570	580	18651	0.465	3.5	2.81	1	17	755	0.3	18	2.08	0.1	18	4249	4.86	0.86	12	1.48
93-06	580	590	18652	0.520	3.4	2.09	1	13	502	0.3	22	1.10	0.1	20	4836	4.38	0.79	12	1.56
93-06	590	600	18653	0.462	3.2	1.21	1	10	128	0.1	19	1.08	0.1	14	4181	2.73	0.26	9	0.95

II-220

MIN-EN LABORATORIES
 705 W. 15th St.
 North Vancouver, B.C. Huckleberry
 Phone: 980-5814

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)		SAMPLE	MN	MO	NA	NI	P	PB	SB	SR	TH	TI	V	ZN	GA	SN	W	CR
HOLE#	START	END	NAME	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM
93-06	450	460	18639	355	62	0.22	1	1000	14	9	84	4	2511	124.8	39	9	2	8	81
93-06	460	470	18640	384	122	0.09	1	830	19	8	43	4	2535	128.2	40	8	2	8	82
93-06	470	480	18641	347	114	0.09	1	790	16	7	41	5	2120	105.0	39	7	2	6	61
93-06	480	490	18642	293	71	0.08	1	910	7	6	33	4	2859	103.2	41	7	2	7	74
93-06	490	500	18643	357	100	0.12	1	950	16	9	43	3	2696	111.7	44	8	3	8	80
93-06	500	510	18644	345	138	0.19	1	800	16	11	90	3	2888	125.5	49	8	2	9	106
93-06	510	520	18645	360	152	0.36	1	830	19	12	154	5	2749	103.9	34	11	3	7	51
93-06	520	530	18646	341	47	0.28	1	960	8	5	98	3	2752	78.4	36	8	3	7	89
93-06	530	540	18647	352	71	0.11	2	730	12	7	64	3	3378	150.8	47	8	2	9	80
93-06	540	550	18648	334	72	0.27	1	840	14	9	65	4	3069	136.7	45	8	3	10	127
93-06	550	560	18649	246	67	0.37	4	800	15	10	83	3	2463	107.0	49	7	2	7	56
93-06	560	570	18650	354	88	0.31	2	890	17	9	83	4	2608	122.5	49	9	2	8	82
93-06	570	580	18651	384	296	0.23	1	920	15	10	61	4	2426	103.9	47	8	1	7	55
93-06	580	590	18652	291	135	0.15	1	770	12	8	76	3	3318	120.1	46	8	2	8	74
93-06	590	600	18653	263	145	0.08	5	590	12	7	56	3	2021	65.0	38	6	1	8	106

122-TP

MIN-EN LABORATORIES
 705 W. 15th St.
 North Vancouver, B.C. Huckleberry
 Phone: 980-5814

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)		SAMPLE	Cu-ASSAY	AG	AL	AS	B	BA	BE	BI	CA	CD	CO	CU	FE	K	LI	MG
HOLE#	START	END	NAME	%	PPM	%	PPM	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	%	%	PPM	%
93-07	65	70	18301	0.661	2.3	3.63	1	12	176	0.8	6	4.39	0.1	16	5587	4.58	0.52	11	1.56
93-07	70	80	18302	1.007	3.5	2.52	1	8	375	0.4	15	1.47	0.1	24	8855	6.31	1.05	17	2.14
93-07	80	90	18303	0.384	0.9	2.27	1	7	390	0.3	18	0.98	0.1	24	3494	5.75	1.15	16	2.31
93-07	90	100	18304	0.172	0.1	2.60	1	8	493	0.4	16	1.32	0.1	23	1644	7.04	0.92	14	1.85
93-07	100	110	18305	0.391	0.6	2.42	1	8	344	0.6	12	2.40	0.1	20	3272	6.12	0.71	10	1.58
93-07	110	120	18306	0.538	2.0	3.03	1	12	342	0.5	14	3.22	0.1	20	5419	6.08	0.79	12	1.56
93-07	120	130	18307	0.817	5.9	2.73	3	10	602	0.5	14	3.47	0.1	16	7365	3.94	0.58	8	1.28
93-07	130	140	18308	0.615	2.5	2.71	1	9	156	0.7	8	3.18	0.1	14	5467	3.46	0.58	9	1.41
93-07	140	150	18309	0.516	2.8	1.32	6	7	72	0.3	7	3.42	0.1	6	4828	2.07	0.19	4	0.39
93-07	150	160	18310	0.386	2.8	2.40	6	11	84	0.6	7	6.83	0.1	10	3854	2.52	0.25	5	0.87
93-07	160	170	18311	0.360	1.0	2.99	1	11	141	0.7	11	2.87	0.1	14	3380	4.30	0.47	9	1.47
93-07	170	180	18312	0.445	2.0	3.37	1	12	285	0.7	13	4.52	0.1	16	4425	5.01	0.61	11	1.73
93-07	180	190	18313	0.545	2.1	2.53	1	14	80	0.8	11	6.75	0.1	11	4907	4.19	0.25	6	0.83
93-07	190	200	18314	0.612	2.9	1.90	1	9	94	0.7	12	4.22	0.1	10	5521	3.56	0.24	5	0.67

222-II

MIN-EN LABORATORIES
 705 W. 15th St.
 North Vancouver, B.C.
 Phone: 980-5814

I.C.P. and Copper assay

New Canamin Resources

Huckleberry

HOLE#	INTERVAL(feet)		SAMPLE	MN	MO	NA	NI	P	PB	SB	SR	TH	TI	V	ZN	GA	SN	W	CR
HOLE#	START	END	NAME	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM
93-07	65	70	18301	679	181	0.11	9	620	24	15	118	4	459	237.6	47	9	2	8	54
93-07	70	80	18302	471	66	0.11	8	640	21	14	39	3	2745	303.6	58	10	3	11	84
93-07	80	90	18303	386	12	0.12	2	610	13	6	33	3	3687	340.2	46	10	3	11	76
93-07	90	100	18304	392	15	0.22	1	550	11	4	35	3	3245	361.4	47	10	3	12	107
93-07	100	110	18305	358	38	0.15	1	560	15	7	38	4	2074	304.4	44	9	2	10	67
93-07	110	120	18306	412	212	0.13	3	670	23	12	45	4	2109	335.8	46	11	2	11	82
93-07	120	130	18307	387	98	0.03	8	790	21	16	54	3	1108	108.3	50	7	1	6	45
93-07	130	140	18308	395	119	0.04	11	470	19	11	36	4	898	134.2	42	8	2	7	66
93-07	140	150	18309	289	427	0.03	3	490	18	11	21	3	154	45.6	26	5	1	4	48
93-07	150	160	18310	562	461	0.03	10	540	29	12	43	1	227	108.6	32	8	2	5	45
93-07	160	170	18311	446	84	0.17	9	560	17	11	56	4	1208	228.4	40	9	2	8	56
93-07	170	180	18312	588	145	0.11	10	610	23	13	51	3	1477	250.1	50	11	2	10	73
93-07	180	190	18313	531	758	0.03	5	520	28	15	42	1	293	182.5	39	10	2	7	54
93-07	190	200	18314	518	419	0.04	5	530	23	13	36	3	332	162.8	34	7	2	7	61

II-223

MIN-EN LABORATORIES
 705 W. 15th St.
 North Vancouver, B.C.
 Phone: 980-5814

I.C.P. and Copper assay

New Canamin Resources

Huckleberry

HOLE#	INTERVAL(feet)	SAMPLE	Cu-ASSAY	AG	AL	AS	B	BA	BE	BI	CA	CD	CO	CU	FE	K	LI	MG	
HOLE#	START	END	NAME	%	PPM	%	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	%	%	PPM	%	
93-08	60	70	18351	0.329	2.6	3.06	1	11	792	0.3	18	1.35	0.1	26	3207	5.37	1.32	14	2.27
93-08	70	80	18352	0.572	3.5	2.15	1	8	602	0.3	18	1.22	0.1	25	5580	5.26	1.16	13	1.98
93-08	80	90	18353	0.490	1.3	2.93	1	10	306	0.2	13	2.27	0.1	25	4910	6.61	1.37	15	2.26
93-08	90	100	18354	0.847	2.7	2.43	1	9	242	0.3	16	2.40	0.1	38	7933	7.53	1.03	13	1.91
93-08	100	110	18355	0.613	1.6	2.79	1	11	350	0.4	21	2.05	0.1	32	5952	8.02	1.31	16	2.60
93-08	110	120	18356	0.345	0.7	3.14	1	13	553	0.5	23	1.96	0.1	32	3431	10.41	1.56	14	2.71
93-08	120	130	18357	0.495	0.6	3.57	1	15	282	0.8	15	2.52	0.1	26	5151	8.55	0.87	11	1.95
93-08	130	140	18358	0.606	2.1	2.20	1	9	205	0.4	15	2.02	0.1	19	5851	5.90	0.72	11	1.68
93-08	140	150	18359	0.414	2.2	2.01	1	9	292	0.4	16	2.46	0.1	21	4199	5.09	0.90	13	1.73
93-08	150	160	18360	0.406	2.8	2.01	1	9	331	0.4	16	2.20	0.1	21	3975	4.48	1.05	13	2.04
93-08	160	170	18361	0.238	2.0	3.08	5	5	335	0.3	4	5.92	0.1	11	2104	2.71	0.53	9	1.04
93-08	170	180	18362	0.274	2.7	2.60	1	13	499	0.2	10	3.54	0.1	16	2425	4.01	0.71	10	1.32
93-08	180	190	18363	0.540	3.7	2.06	1	12	502	0.1	9	1.56	0.1	19	4878	4.05	0.95	13	1.70
93-08	190	200	18364	0.302	2.6	2.27	1	13	547	0.2	11	1.78	0.1	20	2994	4.41	1.08	13	1.80
93-08	200	210	18365	0.567	3.7	2.95	1	15	508	0.3	7	2.88	0.1	17	5227	4.06	0.76	11	1.50
93-08	210	220	18366	0.370	3.1	2.75	1	12	615	0.2	14	1.99	0.1	20	3535	4.69	0.84	12	1.66
93-08	220	230	18367	0.321	2.7	2.61	1	12	711	0.2	13	1.79	0.1	18	3088	4.34	0.94	13	1.68
93-08	230	240	18368	0.477	3.2	1.72	1	8	298	0.1	12	1.76	0.1	15	4283	3.41	0.51	12	1.36
93-08	240	250	18369	0.435	3.3	1.90	1	9	892	0.1	16	1.49	0.1	21	4077	5.48	0.89	11	1.62
93-08	250	260	18370	0.474	3.1	3.11	1	13	579	0.2	14	2.28	0.1	22	4384	5.22	1.30	14	2.59
93-08	260	270	18371	0.493	3.7	1.64	1	9	520	0.1	15	1.58	0.1	19	4280	4.07	0.83	13	1.61
93-08	270	280	18372	0.394	3.2	1.86	1	9	431	0.2	15	1.74	0.1	18	3702	4.18	0.68	13	1.44
93-08	280	290	18373	0.466	3.1	1.35	1	5	397	0.1	12	1.18	0.1	21	4527	5.28	0.65	14	1.10
93-08	290	300	18374	0.415	3.0	1.30	1	6	196	0.2	12	1.41	0.1	15	3769	3.69	0.38	14	1.11
93-08	300	310	18375	0.430	3.0	1.73	1	5	443	0.1	13	1.43	0.1	17	3746	4.33	0.78	13	1.44
93-08	310	320	18376	0.374	2.8	1.20	1	3	158	0.1	7	1.51	0.1	14	3530	3.15	0.35	11	0.94
93-08	320	330	18377	0.442	2.8	1.84	1	5	236	0.3	9	1.69	0.1	16	4051	3.56	0.83	17	2.01
93-08	330	340	18378	0.675	4.1	1.63	1	5	240	0.2	12	2.44	0.1	17	6143	3.42	0.61	14	1.49
93-08	340	350	18379	0.414	3.0	3.97	9	10	573	0.4	16	2.51	0.1	24	3914	5.23	1.44	17	3.07
93-08	350	360	18380	0.316	2.4	1.92	1	3	211	0.3	6	1.87	0.1	13	2983	3.17	0.50	14	1.30
93-08	360	370	18381	0.322	2.3	1.28	1	3	203	0.3	8	1.44	0.1	14	2954	3.13	0.60	11	1.32
93-08	370	380	18382	0.305	2.4	1.65	1	5	580	0.1	14	1.40	0.1	19	2762	4.37	0.91	11	1.60
93-08	380	390	18383	0.416	3.4	2.22	1	8	665	0.1	12	1.68	0.1	17	3953	4.04	0.84	13	1.51
93-08	390	400	18384	0.400	3.0	1.57	1	3	476	0.1	13	1.46	0.1	17	3729	3.81	0.81	13	1.47
93-08	400	410	18385	0.227	1.7	1.69	1	28	468	0.3	3	1.97	0.1	11	2148	3.08	0.54	11	1.00
93-08	410	420	18386	0.341	2.3	1.42	1	27	448	0.3	4	1.56	0.1	13	3156	3.32	0.57	13	1.23
93-08	420	430	18387	0.166	1.5	1.22	1	27	372	0.2	7	1.01	0.1	13	1499	3.23	0.53	12	1.16

H-222

MIN-EN LABORATORIES

705 W. 15th St.

North Vancouver, B.C. Huckleberry

Phone: 980 5814

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)	SAMPLE	MN	MO	NA	NI	P	PB	SB	SR	TH	TI	V	ZN	GA	SN	W	CR	
HOLE#	START	END	NAME	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	
93-08	60	70	18351	317	96	0.19	2	720	15	8	33	4	3403	161.9	39	10	3	9	89
93-08	70	80	18352	280	54	0.11	1	660	14	10	20	3	3082	176.2	43	9	2	9	62
93-08	80	90	18353	297	225	0.28	4	610	16	9	39	4	2959	348.3	39	12	4	13	121
93-08	90	100	18354	356	32	0.22	7	620	24	12	46	3	2602	370.3	54	11	2	12	88
93-08	100	110	18355	449	76	0.11	3	590	16	11	46	3	3582	426.8	52	12	3	13	103
93-08	110	120	18356	424	38	0.21	1	590	8	9	30	3	4638	463.5	60	13	4	14	102
93-08	120	130	18357	353	112	0.36	1	750	16	12	53	4	2454	394.4	47	12	2	15	142
93-08	130	140	18358	307	39	0.21	1	1150	21	11	62	4	2337	255.8	39	10	2	10	88
93-08	140	150	18359	332	101	0.14	5	1100	13	8	43	3	2613	217.8	41	10	2	10	124
93-08	150	160	18360	254	178	0.11	17	720	14	8	40	4	2535	143.2	40	9	2	10	131
93-08	160	170	18361	220	52	0.19	8	420	11	6	56	4	1046	91.6	22	8	3	6	42
93-08	170	180	18362	236	67	0.16	6	780	11	7	77	7	2172	113.3	31	8	3	8	63
93-08	180	190	18363	241	95	0.11	9	890	9	8	63	7	2853	119.9	36	9	3	8	71
93-08	190	200	18364	307	31	0.14	1	890	8	6	55	7	2732	115.8	34	8	3	9	78
93-08	200	210	18365	299	93	0.10	4	1190	9	12	112	8	1895	101.7	35	9	3	9	59
93-08	210	220	18366	342	83	0.12	3	920	11	8	98	8	3083	121.4	38	9	4	11	87
93-08	220	230	18367	302	55	0.19	3	810	14	7	128	7	3010	137.2	32	9	4	9	67
93-08	230	240	18368	275	85	0.11	5	800	12	7	46	6	2646	124.6	35	8	3	8	65
93-08	240	250	18369	335	57	0.12	1	1090	9	7	39	7	3557	152.3	39	9	3	10	77
93-08	250	260	18370	348	153	0.24	10	740	12	10	72	10	3130	199.0	39	11	4	13	134
93-08	260	270	18371	277	94	0.10	5	1400	7	7	44	6	3037	109.8	33	8	3	9	81
93-08	270	280	18372	365	141	0.13	2	880	10	7	37	7	3112	117.2	36	8	3	9	78
93-08	280	290	18373	501	123	0.06	3	580	9	6	29	6	2977	140.5	37	8	3	9	82
93-08	290	300	18374	416	146	0.06	6	700	11	8	26	6	2364	126.4	37	7	2	9	96
93-08	300	310	18375	324	111	0.13	2	800	12	7	31	7	2949	127.3	35	9	3	9	87
93-08	310	320	18376	400	183	0.08	7	760	9	6	25	5	1817	79.0	36	6	2	7	78
93-08	320	330	18377	400	208	0.06	19	900	10	7	31	7	2317	152.7	43	8	3	16	220
93-08	330	340	18378	314	277	0.08	15	870	12	10	54	6	2639	152.6	39	8	3	15	220
93-08	340	350	18379	424	87	0.30	24	810	19	12	73	10	3279	229.4	42	12	4	21	291
93-08	350	360	18380	354	39	0.16	6	750	10	6	46	6	1641	81.9	34	7	2	8	90
93-08	360	370	18381	305	120	0.05	5	720	9	5	25	6	1869	99.1	32	7	2	9	122
93-08	370	380	18382	284	196	0.10	3	650	11	4	31	7	3057	135.0	36	8	3	10	101
93-08	380	390	18383	319	350	0.24	2	860	13	7	41	6	3102	109.9	37	9	4	9	92
93-08	390	400	18384	349	95	0.08	3	810	9	6	27	6	2879	121.0	34	9	4	10	90
93-08	400	410	18385	364	94	0.12	2	630	12	4	44	4	1115	61.0	29	5	2	6	73
93-08	410	420	18386	359	70	0.05	2	930	10	5	27	5	1272	70.5	34	6	2	7	71
93-08	420	430	18387	405	87	0.06	1	510	8	3	17	6	1501	57.2	37	6	1	6	70
93-08	430	440	18388	402	244	0.08	5	860	13	4	54	5	1206	43.5	32	5	2	7	101

11-225

MIN-EN LABORATORIES
 705 W. 15th St.
 North Vancouver, B.C. Huckleberry
 Phone: 980-5814

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)	SAMPLE	Cu-ASSAY	AG	AL	AS	B	BA	BE	BI	CA	CD	CO	CU	FE	K	LI	MG	
HOLE#	START	END	NAME	%	PPM	%	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	%	%	PPM	%	
93-08	440	450	18389	0.199	1.8	1.03	1	27	112	0.2	6	0.90	0.1	8	1918	2.15	0.26	10	0.75
93-08	450	460	18390	0.462	3.5	1.90	1	20	364	0.1	12	1.20	0.1	20	4272	5.04	0.69	12	1.51
93-08	460	470	18391	0.533	3.2	1.76	1	12	442	0.2	7	1.24	0.1	17	4658	4.04	0.80	13	1.59
93-08	470	480	18392	0.424	2.7	1.52	1	10	404	0.2	6	1.19	0.1	15	3816	3.38	0.54	11	1.11
93-08	480	490	18393	0.574	3.2	1.33	1	12	337	0.2	1	1.52	0.1	12	5226	3.36	0.47	12	1.12
93-08	490	500	18394	0.285	2.5	1.46	1	15	331	0.3	5	1.10	0.1	12	2711	2.94	0.59	15	1.33
93-08	500	510	18395	0.305	2.2	1.63	1	14	395	0.3	8	1.17	0.1	15	2955	3.46	0.68	14	1.44
93-08	510	520	18396	0.194	2.1	1.37	1	14	385	0.1	11	0.89	0.1	12	1703	2.57	0.54	11	1.19
93-08	520	530	18397	0.387	3.0	1.35	1	13	396	0.2	12	0.88	0.1	20	3618	3.63	0.59	12	1.25
93-08	530	540	18398	0.350	2.5	2.19	1	13	361	0.3	13	1.31	0.1	19	3334	4.61	0.74	14	1.85
93-08	540	550	18399	0.395	0.7	2.55	1	12	184	0.1	11	1.33	0.1	24	3763	8.27	0.80	11	1.65
93-08	550	560	18400	0.891	2.8	3.06	1	13	212	0.2	11	1.69	0.1	22	7615	6.32	0.71	10	1.47
93-08	560	570	18660	0.571	2.4	2.72	1	15	305	0.4	18	1.85	0.1	17	5237	5.08	0.52	10	1.31
93-08	570	580	18661	0.338	2.2	1.97	6	12	200	0.2	15	1.58	0.1	12	3061	2.83	0.25	9	0.98
93-08	580	590	18662	0.473	4.3	1.80	6	18	259	0.4	15	1.46	0.1	13	4480	3.58	0.30	10	0.98
93-08	590	600	18663	0.410	2.6	1.45	8	12	107	0.3	14	1.36	0.1	13	3704	2.34	0.17	9	1.08
93-08	600	610	18664	0.399	2.8	1.36	2	11	161	0.2	17	1.21	0.1	13	3683	2.45	0.18	10	1.08
93-08	610	620	18665	0.314	2.2	1.39	8	12	157	0.3	13	1.53	0.1	9	2988	2.08	0.22	9	0.99
93-08	620	625	18666	0.260	1.7	1.14	10	10	85	0.4	9	1.61	0.1	7	2301	1.70	0.16	8	0.76

II-22C

MIN-EN LABORATORIES

705 W. 15th St.

North Vancouver, B.C.

Phone: 980-5814

Huckleberry

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)		SAMPLE	MN	MO	NA	NI	P	PB	SB	SR	TH	TI	V	ZN	GA	SN	W	CR
HOLE#	START	END	NAME	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM
93-08	440	450	18389	379	506	0.09	2	280	11	4	32	4	1396	39.9	28	5	2	6	81
93-08	450	460	18390	411	75	0.14	1	820	15	7	48	6	3251	130.4	41	9	3	12	134
93-08	460	470	18391	380	69	0.12	3	840	14	8	31	6	2282	111.4	37	7	3	8	72
93-08	470	480	18392	340	97	0.11	2	710	11	6	65	5	1776	74.8	33	6	2	9	120
93-08	480	490	18393	291	21	0.05	3	960	14	8	37	5	1094	82.8	32	6	1	8	92
93-08	490	500	18394	324	177	0.06	2	680	14	5	30	6	1254	59.9	34	6	2	7	96
93-08	500	510	18395	339	180	0.07	1	1060	9	5	48	6	1708	78.8	33	6	2	8	75
93-08	510	520	18396	282	144	0.10	3	600	12	3	50	5	2126	46.0	26	6	2	7	85
93-08	520	530	18397	347	119	0.09	2	580	13	5	44	5	2506	76.5	36	7	2	7	72
93-08	530	540	18398	459	95	0.14	9	500	14	6	48	8	2749	176.5	37	9	3	11	108
93-08	540	550	18399	464	187	0.22	1	660	9	7	83	8	3341	436.4	38	12	4	14	87
93-08	550	560	18400	361	118	0.23	5	620	16	13	163	7	3132	330.5	49	11	4	14	112
93-08	560	570	18660	379	110	0.18	1	730	16	11	86	3	2418	215.4	72	8	2	9	69
93-08	570	580	18661	303	114	0.12	3	690	12	7	64	3	1812	72.3	39	7	2	6	63
93-08	580	590	18662	324	1017	0.11	2	630	15	11	64	5	1452	69.5	39	7	2	8	91
93-08	590	600	18663	260	247	0.08	6	570	14	8	71	4	1504	76.5	41	6	2	8	105
93-08	600	610	18664	222	164	0.07	5	570	14	7	69	3	1918	82.1	42	7	1	6	71
93-08	610	620	18665	229	421	0.08	4	440	13	7	46	3	1345	76.2	36	7	1	7	99
93-08	620	625	18666	227	308	0.05	4	550	13	7	18	4	434	55.6	34	6	1	6	95

422-11

MIN-EN LABORATORIES
 705 W. 15th St.
 North Vancouver, B.C.
 Phone: 980-5814

I.C.P. and Copper assay

New Canamin Resources

Huckleberry

HOLE#	INTERVAL(feet)	SAMPLE	Cu-ASSAY	AG	AL	AS	B	BA	BE	BI	CA	CD	CO	CU	FE	K	LI	MG	
HOLE#	START	END	NAME	%	PPM	%	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	%	%	PPM	%	
93-09	65	70	18251	0.235	1.6	0.79	1	7	328	0.4	1	1.49	0.1	13	2323	2.25	0.31	7	0.58
93-09	70	80	18252	0.360	2.5	1.16	1	9	421	0.3	2	2.36	0.1	14	3518	2.50	0.45	12	0.98
93-09	80	90	18253	0.352	2.8	1.62	1	8	265	0.3	2	1.81	0.1	19	3539	3.41	0.52	12	1.15
93-09	90	100	18254	0.523	3.2	2.55	1	9	324	0.2	1	1.80	0.1	20	4834	3.67	0.79	14	1.41
93-09	100	110	18255	0.286	2.1	1.29	1	7	189	0.3	2	1.63	0.1	12	2706	2.76	0.38	12	0.95
93-09	110	120	18256	0.180	1.9	0.80	6	6	125	0.2	1	3.33	0.1	6	1572	1.28	0.23	9	0.71
93-09	120	130	18257	0.361	2.1	1.55	1	5	202	0.4	1	1.89	0.1	11	3394	2.44	0.53	17	1.51
93-09	130	140	18258	0.361	2.7	2.04	1	6	296	0.3	3	1.80	0.1	19	3487	4.17	0.77	17	1.45
93-09	140	150	18259	0.634	3.9	1.98	1	6	206	0.2	1	2.03	0.1	18	6038	3.79	0.62	14	1.38
93-09	150	160	18260	0.441	3.2	2.82	1	9	226	0.4	1	2.09	0.1	20	4369	4.64	0.76	17	1.64
93-09	160	170	18261	0.316	2.1	1.09	1	5	166	0.4	1	1.42	0.1	11	3085	3.24	0.31	13	0.64
93-09	170	180	18262	0.355	2.2	1.03	1	4	151	0.3	1	1.39	0.1	12	3028	2.81	0.27	9	0.50
93-09	180	190	18263	0.360	2.6	2.22	1	5	214	0.4	1	2.16	0.1	15	3273	3.59	0.54	12	1.20
93-09	190	200	18264	0.248	2.3	3.24	1	8	277	0.5	6	2.11	0.1	18	2535	4.56	0.85	13	1.65
93-09	200	210	18265	0.258	2.1	3.04	1	8	204	0.5	5	2.37	0.1	16	2293	4.05	0.54	10	1.22
93-09	210	220	18266	0.370	3.2	2.19	1	5	295	0.4	5	2.05	0.1	24	3517	4.13	0.63	15	1.43
93-09	220	230	18267	0.191	2.0	1.68	1	4	500	0.4	8	1.35	0.1	19	1788	3.73	0.63	20	1.35
93-09	230	240	18268	0.383	3.1	1.38	1	2	227	0.3	4	1.45	0.1	22	3622	3.82	0.45	15	1.07
93-09	240	250	18269	0.599	4.2	1.80	1	3	368	0.3	1	1.71	0.1	22	5590	4.17	0.67	15	1.14
93-09	250	260	18270	0.287	2.7	2.04	1	3	570	0.4	7	1.42	0.1	20	2900	3.87	1.01	20	1.59
93-09	260	270	18271	0.409	3.4	1.46	1	2	307	0.3	5	1.63	0.1	23	3953	3.80	0.70	16	1.37
93-09	270	280	18272	0.573	4.3	1.85	1	4	540	0.3	1	1.68	0.1	28	5509	3.86	0.87	16	1.44
93-09	280	290	18273	0.506	4.0	3.28	1	6	824	0.4	7	1.94	0.1	23	5012	4.53	1.38	23	2.37

322-II

MIN-EN LABORATORIES

705 W. 15th St.

North Vancouver, B.C.

Phone: 980-5814

Huckleberry

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)	SAMPLE	MN	MO	NA	NI	P	PB	SB	SR	TH	TI	V	ZN	GA	SN	W	CR	
HOLE#	START	END	NAME	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	
93-09	65	70	18251	447	279	0.05	5	420	16	9	32	5	201	30.4	36	2	2	8	119
93-09	70	80	18252	302	334	0.09	4	560	18	9	57	7	969	64.7	31	5	3	10	141
93-09	80	90	18253	221	73	0.12	1	470	56	6	44	7	2071	81.4	632	7	4	9	97
93-09	90	100	18254	289	36	0.25	4	890	11	7	66	10	1866	117.9	35	8	3	10	99
93-09	100	110	18255	280	173	0.07	2	350	13	5	32	7	1362	83.9	28	6	3	9	112
93-09	110	120	18256	207	260	0.02	2	190	7	4	90	5	443	36.8	22	4	2	7	103
93-09	120	130	18257	362	156	0.03	6	290	7	6	29	8	665	86.4	30	6	2	8	101
93-09	130	140	18258	310	57	0.13	2	580	7	6	52	9	2282	130.6	28	9	3	9	88
93-09	140	150	18259	265	50	0.19	1	840	9	9	48	8	2071	101.0	32	8	3	10	113
93-09	150	160	18260	331	285	0.31	1	880	9	8	61	10	1940	112.4	31	10	4	10	103
93-09	160	170	18261	358	131	0.03	1	770	10	7	27	6	1157	67.3	22	5	2	6	83
93-09	170	180	18262	300	106	0.05	1	810	10	6	27	5	932	62.4	21	4	2	7	94
93-09	180	190	18263	303	40	0.18	2	930	11	6	80	9	1359	89.7	27	8	2	8	91
93-09	190	200	18264	311	84	0.37	1	920	14	6	83	11	2051	117.8	27	10	4	11	129
93-09	200	210	18265	488	20	0.32	1	840	9	5	88	10	1414	95.1	28	8	3	9	94
93-09	210	220	18266	358	49	0.16	1	900	11	8	67	10	2061	103.4	31	9	3	8	71
93-09	220	230	18267	375	119	0.07	1	800	10	3	34	7	2030	78.2	27	8	3	8	87
93-09	230	240	18268	414	54	0.06	1	1020	9	6	33	7	1832	78.6	31	7	3	7	73
93-09	240	250	18269	388	61	0.11	1	670	9	9	63	8	1773	93.1	33	7	3	9	93
93-09	250	260	18270	377	32	0.14	1	830	6	4	41	9	2352	96.4	30	9	3	8	87
93-09	260	270	18271	330	33	0.06	1	1030	10	6	38	8	2173	93.9	32	7	3	9	103
93-09	270	280	18272	477	53	0.07	1	770	11	9	46	8	1799	85.6	33	8	3	7	65
93-09	280	290	18273	536	26	0.24	5	830	13	10	58	12	2774	156.4	45	11	3	12	106

522-II

MIN-EN LABORATORIES
 705 W. 15th St.
 North Vancouver, B.C.
 Phone: 980-5814 Huckleberry

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)	SAMPLE	Cu-ASSAY	AG	AL	AS	B	BA	BE	BI	CA	CD	CO	CU	FE	K	LI	MG	
HOLE#	START	END	NAME	%	PPM	%	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	%	%	PPM	%	
93-10	50	60	18401	0.328	2.1	1.21	1	4	279	0.4	1	2.16	0.1	16	2950	3.05	0.54	11	1.02
93-10	60	70	18402	0.300	2.2	1.61	1	5	287	0.4	3	1.66	0.1	25	2861	3.79	0.71	14	1.35
93-10	70	80	18403	0.398	3.2	2.32	1	7	411	0.5	6	1.75	0.1	20	3749	4.30	0.97	13	1.71
93-10	80	90	18404	0.261	2.4	2.93	2	8	275	0.6	6	2.64	0.1	17	2574	4.27	0.67	12	1.35
93-10	90	100	18405	0.211	2.7	3.12	1	9	567	0.5	11	2.24	0.1	23	2148	4.90	0.81	11	1.67
93-10	100	110	18406	0.319	2.8	3.32	4	9	527	0.4	7	2.44	0.1	19	2976	3.99	0.77	12	1.70
93-10	110	120	18407	0.266	2.6	2.37	1	8	455	0.4	7	2.01	0.1	16	2575	3.89	0.77	12	1.41
93-10	120	130	18408	0.242	2.6	1.64	1	7	455	0.3	10	1.39	0.1	18	2347	4.21	0.83	13	1.45
93-10	130	140	18409	0.210	2.6	3.30	3	10	722	0.4	10	2.09	0.1	17	2013	4.09	0.92	12	1.59
93-10	140	150	18410	0.183	2.3	2.41	1	9	628	0.4	8	1.96	0.1	18	1762	3.58	0.65	12	1.30
93-10	150	160	18411	0.469	3.7	2.30	1	8	671	0.3	8	1.68	0.1	21	4456	4.62	1.01	13	1.59
93-10	160	170	18412	0.340	3.3	1.99	1	8	664	0.3	9	1.58	0.1	40	3250	3.79	0.89	14	1.54
93-10	170	180	18413	0.577	3.6	1.10	1	7	136	0.3	1	1.69	0.1	13	5295	2.82	0.32	13	1.08
93-10	180	190	18414	0.615	3.5	1.21	4	8	168	0.4	1	2.30	0.1	14	5751	2.77	0.36	13	1.06
93-10	190	200	18415	0.172	1.7	1.09	1	6	346	0.4	5	1.50	0.1	10	1571	2.70	0.47	11	0.97
93-10	200	210	18416	0.132	1.3	0.64	10	6	343	0.3	2	1.90	0.1	5	1219	1.51	0.22	6	0.39
93-10	210	220	18417	0.116	1.3	0.79	9	6	252	0.3	2	1.66	0.1	6	1147	1.62	0.29	9	0.64
93-10	220	230	18418	0.224	2.3	0.75	14	10	373	0.4	3	2.59	0.1	23	2137	2.33	0.25	6	0.42
93-10	230	240	18419	0.235	1.8	0.47	18	6	307	0.2	1	1.71	0.1	4	2156	1.06	0.20	4	0.13
93-10	240	250	18420	0.181	1.3	0.64	8	7	246	0.3	1	1.29	0.1	4	1744	1.42	0.24	6	0.24
93-10	250	260	18421	0.502	2.8	0.46	12	6	246	0.2	1	1.74	0.1	4	4364	1.30	0.18	4	0.22
93-10	260	270	18422	0.548	2.9	0.57	3	6	509	0.3	1	1.59	0.1	6	5017	1.99	0.22	6	0.30
93-10	270	280	18423	0.435	2.4	0.85	1	6	203	0.4	1	1.44	0.1	9	4108	2.61	0.27	11	0.74
93-10	280	290	18424	0.458	3.3	1.27	1	6	189	0.4	6	1.27	0.1	16	4568	3.65	0.50	17	1.15
93-10	290	300	18425	0.712	3.5	0.83	1	19	132	0.1	1	1.53	0.1	12	5982	2.15	0.26	29	0.82
93-10	300	310	18426	0.656	3.7	0.86	3	3	52	0.1	1	1.87	0.1	10	5926	2.03	0.15	13	0.88
93-10	310	320	18427	0.597	3.4	1.44	1	4	324	0.2	7	1.53	0.1	16	5057	3.39	0.74	16	1.54
93-10	320	330	18428	0.437	3.3	1.56	1	4	369	0.1	10	1.51	0.1	20	4061	4.68	0.95	16	1.63
93-10	330	340	18429	0.291	2.7	1.49	1	3	249	0.1	9	1.79	0.1	13	2784	2.86	0.32	10	0.98
93-10	340	350	18430	0.413	3.0	1.12	1	2	142	0.1	8	1.55	0.1	13	3717	2.76	0.27	12	0.96
93-10	350	360	18431	0.632	3.8	1.21	1	4	255	0.1	3	1.19	0.1	13	5802	2.60	0.50	14	1.28
93-10	360	370	18432	0.318	2.3	1.29	1	3	348	0.1	7	1.55	0.1	13	2986	2.74	0.51	14	1.25
93-10	370	380	18433	0.267	2.1	1.03	1	2	238	0.1	4	1.49	0.1	12	2343	2.87	0.38	12	1.04
93-10	380	390	18434	0.260	1.9	1.06	1	2	316	0.2	2	1.67	0.1	8	2468	2.43	0.36	11	0.86
93-10	390	400	18435	0.099	1.1	0.94	6	1	268	0.2	3	1.77	0.1	5	860	1.71	0.24	8	0.59
93-10	400	410	18436	0.116	1.1	0.92	2	1	295	0.2	3	1.32	0.1	7	1020	2.08	0.26	8	0.63
93-10	410	420	18437	0.187	1.7	0.83	8	3	145	0.2	3	2.02	0.1	6	1723	1.83	0.15	8	0.56

II-230

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)		SAMPLE	MN	MO	NA	NI	P	PB	SB	SR	TH	TI	V	ZN	GA	SN	W	CR
HOLE#	START	END	NAME	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM
93-10	50	60	18401	333	160	0.05	4	460	5	6	34	7	847	72.0	30	5	3	5	51
93-10	60	70	18402	362	91	0.08	1	360	9	6	29	9	1297	109.6	35	7	4	10	111
93-10	70	80	18403	331	60	0.18	1	830	7	7	53	11	2206	113.0	34	9	4	10	99
93-10	80	90	18404	442	70	0.26	2	870	8	7	108	11	1559	100.7	41	10	4	11	111
93-10	90	100	18405	471	95	0.27	1	930	6	6	153	13	2252	110.1	36	10	4	10	85
93-10	100	110	18406	369	105	0.18	1	850	6	7	244	13	1890	108.0	29	10	4	8	63
93-10	110	120	18407	335	220	0.14	1	700	3	5	102	9	1996	99.3	32	9	4	8	75
93-10	120	130	18408	279	151	0.10	1	820	9	5	43	9	2544	95.8	33	9	4	8	72
93-10	130	140	18409	271	81	0.35	1	870	7	6	121	11	2331	100.7	31	11	4	9	96
93-10	140	150	18410	261	122	0.23	1	790	2	4	100	10	1983	83.9	30	9	3	8	71
93-10	150	160	18411	291	70	0.20	1	800	5	8	45	10	2795	134.0	37	10	4	8	78
93-10	160	170	18412	303	363	0.16	1	830	6	5	52	10	2602	111.7	35	10	5	9	79
93-10	170	180	18413	349	258	0.04	6	950	12	9	27	8	1173	86.6	38	6	3	9	97
93-10	180	190	18414	291	421	0.05	6	870	8	10	45	8	640	79.0	34	7	3	7	78
93-10	190	200	18415	351	175	0.06	2	700	7	4	25	8	1028	62.2	28	6	2	7	90
93-10	200	210	18416	398	304	0.03	4	610	4	4	32	5	216	23.1	23	3	2	5	79
93-10	210	220	18417	306	135	0.05	4	290	5	4	26	6	337	22.8	27	4	1	6	105
93-10	220	230	18418	405	940	0.04	3	640	10	6	43	7	243	26.3	26	5	3	5	77
93-10	230	240	18419	238	287	0.03	4	330	8	6	28	5	73	11.3	22	2	1	6	121
93-10	240	250	18420	308	182	0.03	2	320	4	5	20	5	116	15.0	18	3	1	5	89
93-10	250	260	18421	244	421	0.03	5	450	10	9	30	5	78	15.3	21	3	1	6	112
93-10	260	270	18422	321	280	0.03	4	350	7	9	30	5	250	32.0	22	3	1	6	83
93-10	270	280	18423	378	254	0.04	4	320	9	7	24	5	441	63.0	32	5	2	6	73
93-10	280	290	18424	403	115	0.06	3	660	6	8	21	7	1803	113.6	36	7	3	9	86
93-10	290	300	18425	271	264	0.04	6	790	12	10	28	5	868	78.2	36	4	2	7	96
93-10	300	310	18426	250	240	0.04	8	720	12	9	35	5	885	58.0	37	4	2	6	80
93-10	310	320	18427	319	80	0.06	5	670	12	8	33	6	2083	126.0	37	7	3	10	90
93-10	320	330	18428	296	64	0.07	6	1040	8	6	32	7	2997	155.7	40	10	4	10	72
93-10	330	340	18429	274	82	0.15	3	810	7	5	44	5	2138	66.0	32	6	2	9	108
93-10	340	350	18430	275	148	0.07	7	740	8	6	59	5	1998	72.3	33	6	3	9	117
93-10	350	360	18431	239	543	0.09	5	430	9	8	25	6	1799	68.8	36	7	3	9	103
93-10	360	370	18432	238	210	0.09	3	990	10	5	64	6	1713	78.7	32	7	3	7	69
93-10	370	380	18433	391	258	0.05	1	530	10	4	28	6	995	62.0	34	6	2	7	87
93-10	380	390	18434	302	182	0.06	2	730	9	5	27	5	664	38.0	30	5	1	5	85
93-10	390	400	18435	332	76	0.05	2	350	10	3	27	5	243	22.4	27	4	1	7	121
93-10	400	410	18436	376	84	0.06	1	480	6	3	23	5	366	30.4	33	4	1	6	99
93-10	410	420	18437	383	429	0.08	5	370	11	4	47	5	341	23.3	31	4	2	7	105

182-11

MIN-EN LABORATORIES
 705 W. 15th St.
 North Vancouver, B.C. Huckleberry
 Phone: 980-5814

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)		SAMPLE	Cu-ASSAY	AG	AL	AS	B	BA	BE	BI	CA	CD	CO	CU	FE	K	LI	MG
HOLE#	START	END	NAME	%	PPM	%	PPM	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	%	%	PPM	%
93-10	420	430	18438	0.269	2.2	1.06	7	2	121	0.2	2	1.85	0.1	7	2501	1.82	0.16	9	0.64
93-10	430	440	18439	0.201	1.5	0.66	6	2	82	0.1	4	1.20	0.1	6	1617	1.48	0.13	9	0.58
93-10	440	450	18440	0.249	2.1	0.76	11	1	95	0.1	4	1.24	0.1	8	2208	1.83	0.17	9	0.70
93-10	450	460	18441	0.237	1.8	0.76	2	1	61	0.2	4	1.08	0.1	6	2259	1.50	0.15	10	0.66
93-10	460	470	18442	0.648	3.6	0.83	1	2	83	0.2	7	1.19	0.1	11	6026	2.73	0.18	9	0.74
93-10	470	480	18443	0.890	5.0	1.25	1	4	230	0.1	7	1.16	0.1	16	8332	3.80	0.42	13	1.02
93-10	480	490	18444	1.440	7.7	1.16	4	3	113	0.1	12	1.69	0.1	12	10000	3.05	0.24	9	0.79
93-10	490	500	18445	0.658	3.8	1.07	3	1	168	0.1	5	1.17	0.1	11	6127	2.58	0.32	10	0.96
93-10	500	510	18446	0.479	3.8	1.32	1	2	336	0.1	10	0.84	0.1	16	4717	3.54	0.58	13	1.38
93-10	510	520	18447	1.305	6.0	2.46	1	6	499	0.1	6	1.38	0.1	20	10000	4.12	0.93	15	1.90
93-10	520	530	18448	1.319	6.1	1.63	1	5	167	0.2	2	1.37	0.1	18	10000	3.93	0.42	13	1.37
93-10	530	540	18449	0.659	3.0	1.64	1	4	337	0.1	3	1.14	0.1	18	5625	4.46	0.84	13	1.64
93-10	540	550	18450	1.057	3.9	1.71	1	6	494	0.1	1	1.24	0.1	19	8759	4.72	0.80	15	1.61
93-10	550	560	18670	1.000	4.0	1.53	1	3	389	0.1	1	1.28	0.1	16	9247	3.62	0.55	12	1.27
93-10	560	570	18671	0.704	3.0	1.79	1	3	259	0.2	1	2.49	0.1	11	6830	2.85	0.28	9	0.81
93-10	570	580	18672	0.932	4.8	1.76	1	5	237	0.2	1	1.63	0.1	13	8831	2.97	0.24	10	1.01
93-10	580	590	18673	0.673	3.7	1.62	2	6	204	0.1	8	1.25	0.1	14	5909	2.70	0.26	10	1.18
93-10	590	600	18674	0.592	3.2	1.41	1	4	105	0.1	5	1.26	0.1	13	5377	2.50	0.16	11	1.19
93-10	600	610	18675	0.415	2.5	1.36	1	3	101	0.1	4	1.25	0.1	12	4018	2.65	0.17	11	1.01
93-10	610	620	18676	0.506	2.7	1.16	1	2	119	0.2	4	1.19	0.1	13	4491	3.12	0.14	8	0.75
93-10	620	630	18677	0.560	3.1	2.73	4	8	380	0.3	2	2.21	0.1	16	5267	3.24	0.77	15	2.05

II-232

MIN-EN LABORATORIES
 705 W. 15th St.
 North Vancouver, B.C. Huckleberry
 Phone: 980-5814

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)		SAMPLE	MN	MO	NA	NI	P	PB	SB	SR	TH	TI	ZN	GA	SN	W	CR	
HOLE#	START	END	NAME	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	
93-10	420	430	18438	363	171	0.07	2	380	9	6	59	4	441	28.3	29	4	1	8	114
93-10	430	440	18439	244	100	0.05	4	280	6	4	27	5	554	25.5	25	3	1	5	81
93-10	440	450	18440	269	174	0.05	3	240	11	5	20	5	932	31.2	27	4	1	7	93
93-10	450	460	18441	220	199	0.05	5	330	10	5	21	5	781	32.1	25	4	2	6	94
93-10	460	470	18442	215	142	0.06	4	280	13	10	16	5	1507	75.3	32	6	2	8	95
93-10	470	480	18443	266	234	0.06	5	280	14	13	27	6	2163	106.1	37	7	3	8	64
93-10	480	490	18444	217	199	0.08	4	490	22	22	37	6	1431	53.0	37	6	2	11	141
93-10	490	500	18445	249	60	0.07	4	1060	12	10	29	5	1424	47.0	36	6	2	7	69
93-10	500	510	18446	297	88	0.08	1	760	10	7	30	5	2705	75.1	43	7	3	9	91
93-10	510	520	18447	275	193	0.15	11	930	19	18	154	8	2485	157.7	46	10	3	11	73
93-10	520	530	18448	245	268	0.09	13	770	19	19	64	6	1593	141.1	53	8	3	11	123
93-10	530	540	18449	253	142	0.12	3	910	10	6	40	7	2440	161.8	41	8	4	10	89
93-10	540	550	18450	310	129	0.09	7	810	15	12	75	6	2181	158.5	45	8	4	9	71
93-10	550	560	18670	259	193	0.12	10	590	24	16	73	6	1745	133.4	45	7	4	9	75
93-10	560	570	18671	227	126	0.10	7	360	17	12	69	6	661	76.7	38	5	3	7	80
93-10	570	580	18672	268	271	0.12	10	690	14	13	108	6	1750	79.5	45	6	3	8	90
93-10	580	590	18673	253	509	0.13	10	560	18	12	107	6	1952	91.9	39	7	3	9	100
93-10	590	600	18674	249	301	0.08	9	550	13	8	77	6	1866	89.9	45	6	3	9	99
93-10	600	610	18675	301	87	0.07	6	440	13	6	56	5	1742	77.8	45	5	3	8	86
93-10	610	620	18676	289	89	0.06	7	220	12	7	81	4	1598	68.9	42	5	3	6	70
93-10	620	630	18677	331	529	0.16	17	680	15	10	110	9	1650	140.3	44	9	4	11	121

II-233

MIN-EN LABORATORIES
 705 W. 15th St.
 North Vancouver, B.C.
 Phone: 980-5814

Huckleberry

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)		SAMPLE	Cu-ASSAY	AG	AL	AS	B	BA	BE	BI	CA	CD	CO	CU	FE	K	LI	MG
HOLE#	START	END	NAME	%	PPM	%	PPM	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	%	%	PPM	%
93-11	40	50	18451	0.430	2.5	3.04	1	10	323	0.3	3	2.26	0.1	14	3761	3.88	0.81	15	1.57
93-11	50	60	18452	0.283	2.8	4.05	3	15	271	0.2	9	2.37	0.1	20	2889	4.72	0.87	16	1.69
93-11	60	70	18453	0.264	2.0	2.37	1	8	274	0.2	8	1.55	0.1	16	2567	3.94	0.86	17	1.67
93-11	70	80	18454	0.241	2.4	2.57	1	10	681	0.2	10	2.35	0.1	16	2335	3.88	1.19	17	1.64
93-11	80	90	18455	0.205	1.7	1.63	1	7	760	0.3	5	2.06	0.1	12	1886	2.92	0.80	14	1.24
93-11	90	100	18456	0.313	2.3	2.02	1	8	455	0.3	5	2.33	0.1	18	2903	3.87	0.68	12	1.15
93-11	100	110	18457	0.367	2.3	1.32	1	6	380	0.2	3	1.78	0.1	11	3383	3.06	0.55	12	1.02
93-11	110	120	18458	0.299	1.9	0.89	1	6	471	0.2	1	1.47	0.1	7	2729	2.04	0.35	8	0.45
93-11	120	130	18459	0.358	1.8	0.97	1	5	462	0.2	1	1.55	0.1	10	3167	2.41	0.34	10	0.68
93-11	130	140	18460	0.275	2.1	2.37	4	9	964	0.1	11	1.76	0.1	16	2498	4.04	0.73	12	1.26
93-11	140	150	18461	0.486	3.0	1.78	1	7	987	0.2	5	2.88	0.1	15	4517	3.49	0.75	13	1.27
93-11	150	160	18462	0.321	2.2	1.63	1	8	494	0.2	3	2.28	0.1	12	3222	3.30	0.63	13	1.12
93-11	160	170	18463	0.212	1.4	0.87	1	5	469	0.2	3	1.41	0.1	7	1817	2.04	0.34	10	0.79
93-11	170	180	18464	0.236	1.7	0.68	12	4	479	0.2	1	2.20	0.1	6	2050	1.40	0.27	6	0.48
93-11	180	190	18465	0.830	3.3	0.68	3	5	531	0.2	1	1.56	0.1	6	6514	1.80	0.25	5	0.38
93-11	190	200	18466	0.473	2.5	1.05	8	6	254	0.1	1	1.73	0.1	8	4432	2.19	0.26	9	0.69
93-11	200	210	18467	0.815	3.7	0.79	15	7	287	0.2	1	1.68	0.1	6	7032	1.71	0.23	6	0.40
93-11	210	220	18468	0.656	3.1	0.73	1	8	172	0.2	1	1.70	0.1	8	6164	1.96	0.20	6	0.56
93-11	220	230	18469	0.558	2.6	0.97	1	7	212	0.1	1	1.46	0.1	11	5041	2.33	0.28	11	0.90
93-11	230	240	18470	0.446	2.3	2.04	1	9	530	0.2	1	1.58	0.1	19	4198	4.53	0.92	15	1.70
93-11	240	250	18471	0.634	2.7	1.51	1	8	285	0.2	1	1.51	0.1	17	5675	3.62	0.57	14	1.27
93-11	250	260	18472	0.417	2.3	1.30	1	7	329	0.1	6	1.32	0.1	16	3748	4.04	0.58	13	1.25
93-11	260	270	18473	0.494	2.7	1.26	1	5	215	0.1	1	1.44	0.1	14	4417	2.92	0.38	11	1.15
93-11	270	280	18474	0.471	2.6	1.09	1	5	157	0.2	1	1.66	0.1	14	4226	2.97	0.31	12	1.08
93-11	280	290	18475	0.502	2.8	1.23	1	6	245	0.1	1	1.31	0.1	16	4794	3.45	0.55	12	1.32
93-11	290	300	18476	0.433	2.5	1.54	1	6	269	0.1	1	1.55	0.1	17	3998	3.90	0.78	13	1.54
93-11	300	310	18477	0.479	2.6	1.08	1	6	129	0.1	1	1.81	0.1	10	4321	2.14	0.29	11	1.00
93-11	310	320	18478	0.424	2.7	1.33	1	6	166	0.1	1	1.69	0.1	12	3964	2.86	0.26	10	0.93
93-11	320	330	18479	0.456	2.9	1.28	1	6	228	0.1	1	1.78	0.1	18	4195	3.69	0.46	11	1.19
93-11	330	340	18480	0.495	3.2	1.71	1	7	399	0.1	1	1.63	0.1	19	4563	4.34	0.78	13	1.58
93-11	340	350	18481	0.542	2.9	1.82	1	5	278	0.1	1	1.78	0.1	17	4844	3.95	0.54	11	1.25
93-11	350	360	18482	0.869	3.7	1.82	1	7	741	0.1	1	1.59	0.1	21	7444	4.67	0.76	12	1.46
93-11	360	370	18483	1.487	6.3	1.37	1	5	259	0.1	1	1.84	0.1	21	10000	4.10	0.34	10	1.07
93-11	370	380	18484	1.454	6.8	1.33	1	8	214	0.1	1	2.07	0.1	24	10000	5.17	0.49	12	1.49
93-11	380	390	18485	0.814	4.5	1.64	1	8	256	0.1	1	2.69	0.1	21	7441	4.17	0.68	13	1.75
93-11	390	400	18486	1.075	4.6	1.85	1	7	325	0.1	1	1.99	0.1	23	9567	4.65	0.81	13	1.90
93-11	400	410	18487	1.843	7.0	0.96	1	5	143	0.1	1	2.25	0.1	23	10000	4.09	0.29	9	1.08

II-234

MIN-EN LABORATORIES
 705 W. 15th St.
 North Vancouver, B.C. Huckleberry
 Phone: 980-5814

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)		SAMPLE	MN	MO	NA	NI	P	PB	SB	SR	TH	TI	ZN	GA	SN	W	CR	
HOLE#	START	END	NAME	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	
93-11	40	50	18451	409	45	0.26	2	850	14	12	54	8	1313	103.1	36	8	3	8	85
93-11	50	60	18452	470	541	0.46	1	930	13	7	72	10	2192	115.8	32	11	5	10	86
93-11	60	70	18453	395	25	0.20	1	950	6	5	41	8	2023	112.1	33	8	4	9	105
93-11	70	80	18454	572	105	0.16	1	910	31	6	47	8	2150	107.5	67	9	4	12	81
93-11	80	90	18455	699	174	0.05	1	900	24	5	39	6	1176	81.0	49	6	3	8	93
93-11	90	100	18456	592	65	0.05	1	1040	17	7	38	6	1223	86.9	47	7	3	7	71
93-11	100	110	18457	512	157	0.06	1	910	15	6	35	6	1009	70.5	34	6	2	7	89
93-11	110	120	18458	575	155	0.03	3	860	9	5	34	4	314	48.2	26	3	2	6	105
93-11	120	130	18459	500	221	0.03	2	650	9	6	37	5	416	67.1	29	4	1	6	83
93-11	130	140	18460	409	111	0.20	1	700	8	6	51	8	1910	112.6	32	8	4	10	109
93-11	140	150	18461	539	93	0.06	4	920	19	9	77	6	1413	94.0	41	7	3	9	109
93-11	150	160	18462	472	233	0.04	3	830	14	7	45	6	907	78.4	39	6	2	7	95
93-11	160	170	18463	488	244	0.03	1	560	12	4	30	4	550	45.0	29	4	1	5	83
93-11	170	180	18464	463	115	0.02	3	660	13	5	35	4	185	22.8	24	3	1	5	70
93-11	180	190	18465	324	420	0.03	4	330	12	10	29	4	129	16.8	27	3	2	5	82
93-11	190	200	18466	352	146	0.06	6	710	11	8	32	6	309	39.2	32	5	3	7	93
93-11	200	210	18467	301	549	0.04	5	480	15	12	29	5	111	21.5	27	3	2	6	103
93-11	210	220	18468	290	578	0.04	3	410	11	9	25	4	198	25.4	29	3	2	6	86
93-11	220	230	18469	264	260	0.05	3	430	12	7	27	5	819	61.1	31	4	3	7	94
93-11	230	240	18470	332	178	0.09	1	390	12	9	48	11	2296	167.6	36	9	6	11	76
93-11	240	250	18471	308	102	0.07	3	860	14	9	36	7	1633	128.4	35	6	4	10	113
93-11	250	260	18472	326	194	0.05	1	290	10	6	29	7	1917	137.7	35	7	4	9	83
93-11	260	270	18473	214	162	0.08	4	890	9	6	39	6	1609	77.5	32	5	4	7	73
93-11	270	280	18474	263	137	0.06	1	510	4	6	34	6	1395	81.0	32	6	4	7	72
93-11	280	290	18475	246	268	0.05	4	490	9	8	29	8	2035	98.5	34	7	4	7	77
93-11	290	300	18476	281	269	0.08	4	900	4	6	42	8	2062	124.9	31	8	5	9	77
93-11	300	310	18477	253	253	0.08	4	700	9	7	40	6	1108	60.0	32	5	3	7	65
93-11	310	320	18478	295	61	0.12	4	820	8	6	43	7	1468	62.4	36	6	3	7	77
93-11	320	330	18479	274	98	0.09	1	660	8	6	44	8	2550	123.7	36	7	5	9	97
93-11	330	340	18480	282	491	0.11	4	990	10	6	46	10	2900	162.7	38	9	6	10	90
93-11	340	350	18481	311	146	0.18	1	670	9	6	57	8	2142	131.5	35	8	5	9	92
93-11	350	360	18482	294	186	0.15	1	630	9	11	38	9	2268	144.7	42	8	5	13	76
93-11	360	370	18483	248	218	0.11	4	920	15	17	41	6	1784	92.1	51	7	4	9	78
93-11	370	380	18484	255	659	0.07	6	850	14	17	49	9	2125	140.3	55	9	6	11	80
93-11	380	390	18485	291	416	0.12	10	1020	13	12	68	9	2334	155.5	47	9	5	12	122
93-11	390	400	18486	277	222	0.15	11	850	9	13	49	10	2475	175.9	56	9	5	13	126
93-11	400	410	18487	236	152	0.04	3	830	18	21	48	8	1393	102.8	56	6	4	8	76

11-235

MIN-EN LABORATORIES

705 W. 15th St.

North Vancouver, B.C. Huckleberry

Phone: 980-5814

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)		SAMPLE	Cu-ASSAY	AG	AL	AS	B	BA	BE	BI	CA	CD	CO	CU	FE	K	LI	MG
HOLE#	START	END	NAME	%	PPM	%	PPM	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	%	%	PPM	%
93-11	410	420	18488	0.495	3.2	0.94	2	5	272	0.2	1	2.04	0.1	12	4217	2.37	0.38	11	1.28
93-11	420	430	18489	0.816	3.6	1.20	1	5	242	0.1	1	2.08	0.1	17	7198	3.57	0.53	12	1.51
93-11	430	440	18490	0.241	1.7	0.92	1	4	231	0.2	1	1.70	0.1	11	2063	2.53	0.18	11	1.24
93-11	440	450	18491	0.177	1.2	0.92	1	4	309	0.2	1	1.57	0.1	10	1523	2.51	0.19	10	1.11
93-11	450	460	18492	0.202	1.3	0.94	1	6	282	0.3	1	1.48	0.1	11	1740	2.57	0.17	10	1.25
93-11	460	470	18493	0.458	2.3	0.95	1	6	285	0.3	1	1.75	0.1	14	4014	2.50	0.24	11	1.28
93-11	470	480	18494	0.341	2.0	0.99	1	7	310	0.3	1	1.62	0.1	13	2997	2.46	0.23	11	1.29
93-11	480	490	18495	0.286	2.1	0.96	4	5	298	0.3	1	1.58	0.1	14	2521	2.69	0.22	10	1.23
93-11	490	500	18496	0.373	2.3	0.92	1	7	232	0.3	1	1.79	0.1	12	3429	2.46	0.20	10	1.17
93-11	500	510	18497	0.404	2.4	1.01	8	10	373	0.3	1	2.20	0.1	12	3462	2.32	0.28	10	1.17
93-11	510	520	18498	0.468	2.7	1.05	6	7	595	0.3	1	2.13	0.1	13	4246	2.34	0.38	12	1.29

II-236

MIN-EN LABORATORIES

705 W. 15th St.

North Vancouver, B.C.

Phone: 980-5814

Huckleberry

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)		SAMPLE	MN	MO	NA	NI	P	PB	SB	SR	TH	TI	V	ZN	GA	SN	W	CR
HOLE#	START	END	NAME	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM
93-11	410	420	18488	241	595	0.05	8	870	10	6	61	8	1352	67.5	35	6	4	8	105
93-11	420	430	18489	222	456	0.06	6	790	9	10	55	11	1738	105.4	42	8	5	10	103
93-11	430	440	18490	309	267	0.05	4	890	8	3	56	9	872	65.8	42	5	3	7	92
93-11	440	450	18491	298	290	0.06	5	800	11	4	59	8	739	65.8	42	5	3	8	121
93-11	450	460	18492	300	115	0.05	5	950	6	3	44	9	883	81.5	43	5	3	7	99
93-11	460	470	18493	283	194	0.05	11	990	4	6	49	9	776	60.3	43	4	4	8	110
93-11	470	480	18494	248	290	0.06	8	970	4	4	68	10	1097	69.6	42	5	4	8	113
93-11	480	490	18495	252	72	0.06	7	960	5	4	57	10	1616	77.7	44	6	4	9	123
93-11	490	500	18496	286	206	0.05	9	920	6	6	72	9	919	71.9	42	5	3	8	93
93-11	500	510	18497	273	1077	0.06	8	920	6	5	83	11	839	72.8	40	6	5	9	119
93-11	510	520	18498	260	335	0.06	10	980	6	6	84	11	876	63.5	36	6	4	8	118

II-237

MIN-EN LABORATORIES
 705 W. 15th St.
 North Vancouver, B.C.
 Phone: 980-5814

Huckleberry

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)		SAMPLE	Cu-ASSAY	AG	AL	AS	B	BA	BE	BI	CA	CD	CO	CU	FE	K	LI	MG
HOLE#	START	END	NAME	%	PPM	%	PPM	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	%	%	PPM	%
93-12	50	60	18551	0.145	1.7	2.05	1	10	822	0.5	6	3.59	0.1	24	1248	3.92	0.19	6	1.36
93-12	60	70	18552	0.079	1.6	2.15	1	11	544	0.5	8	3.64	0.1	26	696	3.60	0.21	10	1.35
93-12	70	80	18553	0.044	1.5	2.76	3	11	447	0.6	9	3.95	0.1	32	409	4.58	0.16	8	1.34
93-12	80	90	18554	0.163	3.2	0.63	20	9	504	0.3	4	9.20	0.1	7	1467	1.36	0.23	4	1.25
93-12	90	100	18555	0.187	1.8	0.46	13	8	311	0.2	1	3.33	0.1	3	1593	0.58	0.22	2	0.12
93-12	100	110	18556	0.042	1.2	0.34	24	5	384	0.2	4	2.77	0.1	2	352	0.22	0.20	1	0.05
93-12	110	120	18557	0.111	1.3	0.35	15	5	387	0.2	3	2.71	0.1	2	975	0.46	0.20	1	0.07
93-12	120	130	18558	0.085	1.2	0.55	8	4	307	0.2	4	2.30	0.1	2	745	0.33	0.23	1	0.11
93-12	130	140	18559	0.166	1.6	0.77	6	4	306	0.2	1	2.83	0.1	4	1490	0.84	0.26	2	0.26
93-12	140	150	18560	0.482	3.2	3.23	6	9	127	0.7	1	2.87	0.1	10	4840	1.97	0.14	12	1.66
93-12	150	160	18561	0.490	2.9	3.46	10	11	140	0.6	1	2.45	0.1	14	4846	2.67	0.17	14	2.00
93-12	160	170	18562	0.025	2.1	4.29	6	13	313	0.8	17	2.81	0.1	34	268	5.26	0.11	16	3.13
93-12	170	180	18563	0.481	3.1	1.94	1	6	153	0.5	1	2.14	0.1	13	4548	3.01	0.20	12	1.26
93-12	180	190	18564	0.643	4.1	2.18	1	6	32	0.5	1	2.14	0.1	13	6539	2.55	0.09	14	1.55
93-12	190	200	18565	0.745	3.9	1.70	1	4	106	0.4	1	2.44	0.1	10	6818	2.09	0.08	10	1.24
93-12	200	210	18566	0.350	2.1	0.72	9	2	31	0.2	1	2.00	0.1	7	3271	1.43	0.10	9	0.75
93-12	210	220	18567	0.476	3.0	0.87	1	1	56	0.3	1	1.81	0.1	12	4472	2.59	0.10	9	0.89
93-12	220	230	18568	0.591	3.7	0.84	1	1	53	0.2	1	1.46	0.1	13	5545	2.69	0.13	9	0.80
93-12	230	240	18569	0.750	4.0	0.83	15	1	25	0.1	1	1.65	0.1	12	6957	1.87	0.07	7	0.75
93-12	240	250	18570	0.549	2.9	0.83	8	1	28	0.2	1	1.89	0.1	9	5302	1.71	0.08	9	0.84
93-12	250	260	18571	0.604	5.1	0.99	5	1	54	0.3	1	2.15	0.1	9	5551	2.19	0.12	9	0.86
93-12	260	270	18572	0.372	2.6	1.33	21	3	145	0.4	1	4.31	0.1	7	3319	1.48	0.11	9	0.77
93-12	270	275	18573	0.314	1.8	0.66	7	1	45	0.2	1	2.13	0.1	6	2786	1.45	0.05	9	0.78

II-238

MIN-EN LABORATORIES
 705 W. 15th St.
 North Vancouver, B.C. Huckleberry
 Phone: 980-5814

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)		SAMPLE	MN	MO	NA	NI	P	PB	SB	SR	TH	TI	V	ZN	GA	SN	W	CR
HOLE#	START	END	NAME	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM
93-12	50	60	18551	605	27	0.20	75	1190	11	4	141	12	1236	98.0	60	8	5	9	105
93-12	60	70	18552	648	61	0.21	81	1160	16	5	140	14	1057	94.1	67	8	5	9	116
93-12	70	80	18553	703	17	0.22	88	1530	18	5	156	15	1241	122.2	80	9	5	11	133
93-12	80	90	18554	1745	117	0.03	11	230	31	9	61	5	92	19.9	32	5	2	5	47
93-12	90	100	18555	445	134	0.05	4	270	16	7	38	6	36	7.5	12	2	1	3	41
93-12	100	110	18556	346	82	0.06	5	160	20	15	36	5	7	3.4	17	2	1	3	36
93-12	110	120	18557	256	311	0.05	3	210	14	8	34	5	20	5.6	13	2	1	3	44
93-12	120	130	18558	246	98	0.07	4	170	17	7	29	6	21	6.3	8	2	1	4	47
93-12	130	140	18559	343	93	0.08	10	230	15	6	40	6	134	20.5	13	3	2	4	61
93-12	140	150	18560	395	205	0.07	13	680	20	12	84	16	210	64.8	43	8	4	7	66
93-12	150	160	18561	514	68	0.10	36	1000	22	12	92	17	438	75.6	49	9	4	9	71
93-12	160	170	18562	1119	17	0.19	109	1590	18	6	143	23	2307	144.0	81	11	8	12	117
93-12	170	180	18563	405	46	0.06	11	510	15	8	42	11	360	77.0	38	6	3	7	54
93-12	180	190	18564	377	52	0.08	20	1490	18	9	50	12	926	66.2	47	7	3	7	62
93-12	190	200	18565	333	96	0.06	23	1240	13	9	57	10	526	52.9	41	5	2	5	45
93-12	200	210	18566	320	118	0.07	16	560	17	8	24	8	295	35.8	33	3	2	6	85
93-12	210	220	18567	343	56	0.07	25	750	16	8	26	10	1190	63.5	37	5	3	7	67
93-12	220	230	18568	346	112	0.09	22	470	17	10	24	8	1384	67.3	42	6	3	8	76
93-12	230	240	18569	249	82	0.10	28	970	22	14	31	8	1110	45.2	43	4	3	10	149
93-12	240	250	18570	302	80	0.09	22	770	17	9	28	7	758	46.0	46	4	2	9	121
93-12	250	260	18571	358	172	0.05	16	940	12	8	32	9	317	46.7	35	4	3	9	127
93-12	260	270	18572	467	358	0.06	13	900	22	7	74	9	33	35.4	34	5	2	6	68
93-12	270	275	18573	274	101	0.06	13	540	11	5	28	7	308	39.4	34	4	2	8	108

II-239

MIN-EN LABORATORIES
 705 W. 15th St.
 North Vancouver, B.C. Huckleberry
 Phone: 980-5814

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)		SAMPLE	Cu-ASSAY	AG	AL	AS	B	BA	BE	BI	CA	CD	CO	CU	FE	K	LI	MG
HOLE#	START	END	NAME	%	PPM	%	PPM	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	%	%	PPM	%
93-13	30	40	18701	1.043	4.5	0.93	1	7	74	0.1	1	2.41	0.1	19	8748	2.91	0.22	11	1.25
93-13	40	50	18702	0.762	4.5	1.20	1	8	208	0.1	4	1.75	0.1	17	6691	3.12	0.43	10	1.42
93-13	50	60	18703	0.504	3.4	0.92	1	7	95	0.1	4	1.64	0.1	12	4253	2.50	0.19	8	1.08
93-13	60	70	18704	0.768	4.0	1.10	1	8	92	0.1	4	2.27	0.1	16	6717	2.87	0.25	10	1.38
93-13	70	80	18705	0.584	3.8	1.36	1	7	217	0.1	6	1.31	0.1	15	5324	3.05	0.32	11	1.39
93-13	80	90	18706	0.402	3.2	1.41	1	7	267	0.1	12	1.43	0.1	16	3505	3.15	0.36	9	1.30
93-13	90	100	18707	0.715	4.1	1.26	1	8	103	0.1	1	1.62	0.1	12	6310	2.49	0.21	11	1.29
93-13	100	110	18708	0.399	3.4	1.00	3	8	51	0.1	7	1.50	0.1	11	3661	2.20	0.11	10	0.99
93-13	110	120	18709	0.220	2.2	1.08	9	8	50	0.1	8	2.21	0.1	9	1860	1.52	0.10	10	1.05
93-13	120	130	18710	0.162	2.0	1.06	7	8	58	0.1	7	1.85	0.1	8	1407	1.39	0.08	8	0.80
93-13	130	140	18711	0.176	2.1	0.97	6	8	75	0.2	7	2.05	0.1	7	1526	1.27	0.09	7	0.77
93-13	140	150	18712	0.257	2.6	1.04	6	8	50	0.1	9	1.57	0.1	11	2289	1.90	0.09	8	0.90
93-13	150	160	18713	0.264	2.4	1.57	1	9	179	0.1	8	1.60	0.1	12	2310	2.54	0.21	10	1.16
93-13	160	170	18714	0.253	1.9	1.14	1	6	180	0.1	5	1.57	0.1	10	2248	2.32	0.26	8	1.08
93-13	170	180	18715	0.127	1.7	0.90	22	7	351	0.3	3	2.47	0.1	6	982	1.34	0.20	8	0.42
93-13	180	190	18716	0.093	1.2	0.66	4	5	480	0.2	2	1.97	0.1	4	758	1.07	0.20	5	0.42
93-13	190	200	18717	0.102	1.1	0.54	10	4	324	0.2	1	1.56	0.1	4	867	0.97	0.18	5	0.43
93-13	200	210	18718	0.061	1.8	2.09	6	8	588	0.3	10	1.85	0.1	19	552	3.10	0.19	7	1.87
93-13	210	220	18719	0.152	2.3	3.13	5	10	454	0.3	12	2.63	0.1	21	1283	3.61	0.30	13	2.47
93-13	220	230	18720	0.247	2.3	1.24	12	6	133	0.2	5	2.04	0.1	8	2305	1.58	0.29	10	1.03
93-13	230	240	18721	0.218	2.2	0.96	2	6	127	0.2	9	1.51	0.1	13	2068	2.56	0.17	11	1.20
93-13	240	250	18722	0.115	1.6	1.01	1	6	160	0.2	12	1.34	0.1	13	1096	2.95	0.18	12	1.21
93-13	250	260	18723	0.162	1.6	1.09	1	4	388	0.2	5	1.79	0.1	11	1321	2.54	0.22	11	1.07
93-13	260	270	18724	0.131	1.8	0.81	8	4	335	0.1	7	2.36	0.1	6	1111	1.14	0.17	9	0.67
93-13	270	280	18725	0.132	1.6	0.72	5	2	46	0.1	10	1.27	0.1	9	1202	1.33	0.08	9	0.81
93-13	280	290	18726	0.155	1.5	0.93	3	1	191	0.3	4	1.81	0.1	8	1366	1.75	0.20	11	0.97
93-13	290	297	18727	0.200	1.4	0.90	1	1	299	0.2	4	1.44	0.1	10	1697	2.36	0.28	11	1.14

II-24c

MIN-EN LABORATORIES
 705 W. 15th St.
 North Vancouver, B.C. Huckleberry
 Phone: 980-5814

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)		SAMPLE	MN	MO	NA	NI	P	PB	SB	SR	TH	TI	V	ZN	GA	SN	W	CR
HOLE#	START	END	NAME	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM
93-13	30	40	18701	223	113	0.05	23	1140	18	13	38	6	1589	95.2	55	6	3	12	80
93-13	40	50	18702	431	40	0.09	16	640	14	10	31	7	2286	127.2	54	7	3	12	80
93-13	50	60	18703	327	66	0.08	11	800	9	6	33	6	1775	94.4	40	6	3	11	83
93-13	60	70	18704	412	86	0.07	30	840	14	11	35	7	1922	100.1	55	7	3	14	165
93-13	70	80	18705	405	54	0.11	19	520	16	8	74	7	2443	104.5	51	7	3	12	124
93-13	80	90	18706	380	29	0.11	13	910	10	5	68	6	2963	114.4	42	8	4	12	136
93-13	90	100	18707	429	294	0.06	21	990	18	11	38	7	1256	76.0	48	6	3	10	98
93-13	100	110	18708	367	116	0.07	7	780	13	6	41	6	1533	57.6	39	6	3	10	118
93-13	110	120	18709	323	46	0.06	8	1110	11	4	56	7	1269	54.9	33	5	2	8	99
93-13	120	130	18710	288	74	0.08	6	660	9	3	67	5	1321	45.4	29	5	2	8	120
93-13	130	140	18711	269	212	0.07	6	540	9	4	129	6	1122	42.3	29	5	2	9	103
93-13	140	150	18712	408	24	0.08	6	460	11	4	48	6	1713	59.3	35	5	3	10	119
93-13	150	160	18713	363	40	0.10	5	390	12	5	53	7	1926	78.6	37	7	3	8	75
93-13	160	170	18714	367	22	0.07	5	340	7	4	34	6	1161	88.3	37	6	2	9	111
93-13	170	180	18715	287	122	0.03	5	250	29	5	26	5	81	24.1	96	4	1	5	78
93-13	180	190	18716	240	51	0.04	2	290	8	2	22	4	97	22.1	21	3	1	6	110
93-13	190	200	18717	220	69	0.04	4	270	10	3	21	4	91	19.7	20	3	1	5	83
93-13	200	210	18718	504	24	0.29	56	980	12	2	207	9	1716	88.4	49	8	3	10	129
93-13	210	220	18719	663	37	0.29	59	890	14	5	245	10	2105	109.6	57	10	4	11	106
93-13	220	230	18720	284	226	0.11	7	200	8	5	32	6	916	43.9	28	6	2	9	139
93-13	230	240	18721	255	90	0.07	10	940	10	4	62	8	1829	86.4	35	7	3	8	92
93-13	240	250	18722	333	46	0.07	8	1010	8	2	50	8	1691	86.6	42	7	3	8	116
93-13	250	260	18723	329	25	0.06	9	830	9	3	43	9	880	68.7	46	6	2	8	103
93-13	260	270	18724	312	160	0.05	5	550	13	3	49	5	838	34.8	32	4	2	7	100
93-13	270	280	18725	248	59	0.09	5	800	9	2	32	5	1746	52.0	25	4	2	8	101
93-13	280	290	18726	318	69	0.06	7	860	8	3	35	6	842	55.6	30	5	2	9	142
93-13	290	297	18727	291	91	0.05	9	850	3	3	25	8	984	70.5	33	5	2	7	107

112-II

MIN-EN LABORATORIES
 705 W. 15th St.
 North Vancouver, B.C.
 Phone: 980-5814

Huckleberry

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)		SAMPLE	Cu-ASSAY	AG	AL	AS	B	BA	BE	BI	CA	CD	CO	CU	FE	K	LI	MG
HOLE#	START	END	NAME	%	PPM	%	PPM	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	%	%	PPM	%
93-14	30	40	18751	0.760	3.0	1.36	1	6	95	0.2	1	2.71	0.1	18	6618	4.05	0.33	11	1.43
93-14	40	50	18752	0.850	3.3	0.76	1	5	23	0.2	1	2.65	0.1	14	6815	2.82	0.09	8	0.92
93-14	50	60	18753	0.916	3.4	1.50	1	6	113	0.2	1	2.69	0.1	25	7633	5.65	0.37	10	1.27
93-14	60	70	18754	0.327	1.6	1.37	1	6	96	0.2	1	2.01	0.1	14	2909	3.17	0.33	10	1.28
93-14	70	80	18755	0.494	2.6	0.86	1	5	60	0.2	1	1.76	0.1	12	4232	2.52	0.17	8	1.00
93-14	80	90	18756	0.530	2.4	0.71	1	5	21	0.1	1	2.30	0.1	10	4722	1.90	0.08	8	0.86
93-14	90	100	18757	0.482	2.5	0.82	1	5	39	0.2	1	2.58	0.1	11	4154	2.05	0.12	9	0.99
93-14	100	110	18758	0.367	1.7	0.68	1	4	91	0.1	1	1.66	0.1	12	3311	2.78	0.15	7	0.76
93-14	110	120	18759	0.603	2.6	0.95	1	4	203	0.1	1	1.77	0.1	16	5638	3.48	0.37	10	1.18
93-14	120	130	18760	0.567	2.2	0.81	1	4	79	0.2	1	2.06	0.1	11	4841	2.56	0.16	8	0.96
93-14	130	140	18761	0.705	2.9	0.88	1	4	70	0.2	1	2.32	0.1	12	6363	2.65	0.15	8	0.84
93-14	140	150	18762	0.740	3.1	0.81	1	4	51	0.1	1	2.13	0.1	13	6444	2.43	0.14	9	1.01
93-14	150	160	18763	0.527	2.4	0.99	1	4	47	0.1	1	2.00	0.1	12	4567	2.17	0.11	9	0.97
93-14	160	170	18764	0.392	2.0	1.17	1	5	58	0.2	1	2.03	0.1	12	3278	2.26	0.12	10	1.11
93-14	170	180	18765	0.402	2.4	1.27	1	5	139	0.2	1	2.26	0.1	13	3613	2.46	0.26	11	1.30
93-14	180	190	18766	0.323	2.2	1.97	1	7	150	0.1	1	2.06	0.1	14	3099	2.71	0.29	11	1.37
93-14	190	200	18767	0.344	2.0	2.20	1	7	104	0.2	1	2.19	0.1	15	3048	2.92	0.24	11	1.25
93-14	200	210	18768	0.463	2.0	1.27	1	4	116	0.1	1	2.06	0.1	15	3959	3.44	0.24	11	1.29
93-14	210	220	18769	0.550	2.4	0.99	1	5	34	0.1	1	2.04	0.1	15	4805	3.30	0.11	10	1.06
93-14	220	230	18770	0.392	2.2	1.13	1	6	96	0.2	2	1.35	0.1	17	3662	4.25	0.25	10	1.10
93-14	230	240	18771	0.465	2.9	1.50	1	5	283	0.3	5	1.56	0.1	17	4003	4.65	0.41	11	1.32
93-14	240	250	18772	0.259	1.1	1.52	1	5	62	0.2	1	1.76	0.1	11	2394	2.95	0.09	8	0.97
93-14	250	260	18773	0.152	1.2	2.25	1	6	467	0.4	6	2.43	0.1	24	1332	4.15	0.23	8	2.18
93-14	260	270	18774	0.503	2.2	1.36	1	6	146	0.1	1	2.06	0.1	16	4873	4.02	0.21	11	1.20
93-14	270	280	18775	0.390	1.7	0.86	1	4	143	0.1	1	1.66	0.1	12	3431	2.44	0.23	9	1.05
93-14	280	290	18776	0.195	1.3	0.70	1	4	52	0.1	6	1.68	0.1	11	1671	2.08	0.11	6	0.82
93-14	290	300	18777	0.373	1.8	1.36	1	6	152	0.1	4	1.52	0.1	16	3465	3.77	0.29	7	1.03
93-14	300	310	18778	0.258	2.0	0.96	1	4	127	0.1	12	1.77	0.1	15	2162	2.67	0.15	8	1.00
93-14	310	320	18779	0.178	1.6	1.51	1	6	172	0.1	10	1.94	0.1	13	1488	2.36	0.22	9	1.17
93-14	320	330	18780	0.135	1.6	1.71	1	7	198	0.2	13	1.63	0.1	16	1141	3.59	0.32	8	1.09
93-14	330	340	18781	0.151	1.3	1.80	1	7	121	0.2	9	1.68	0.1	16	1343	3.63	0.30	7	1.01
93-14	340	350	18782	0.196	1.6	2.19	1	7	209	0.3	11	1.51	0.1	21	1747	5.16	0.49	9	1.30
93-14	350	360	18783	0.176	1.6	1.68	1	7	383	0.1	9	1.46	0.1	17	1568	3.78	0.40	9	1.10
93-14	360	370	18784	0.338	2.2	1.06	1	5	77	0.2	3	1.31	0.1	15	3016	3.35	0.18	7	0.97
93-14	370	380	18785	0.192	1.5	1.54	1	6	73	0.2	9	1.80	0.1	12	1601	3.00	0.12	6	0.83
93-14	380	390	18786	0.182	1.3	1.54	1	6	483	0.1	11	1.37	0.1	16	1493	3.49	0.34	8	1.11
93-14	390	400	18787	0.188	1.7	1.47	1	5	167	0.2	9	1.83	0.1	13	1679	2.60	0.20	9	0.99

27-272

MIN-EN LABORATORIES
 705 W. 15th St.
 North Vancouver, B.C.
 Phone: 980-5814

Huckleberry

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)		SAMPLE	MN	MO	NA	NI	P	PB	SB	SR	TH	TI	V	ZN	GA	SN	W	CR
HOLE#	START	END	NAME	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM
93-14	30	40	18751	363	125	0.06	19	1320	11	9	58	9	1281	142.1	50	7	4	11	81
93-14	40	50	18752	264	231	0.04	13	2260	20	9	57	7	721	62.0	52	5	3	6	73
93-14	50	60	18753	320	88	0.13	18	1530	10	11	67	9	1550	149.7	59	8	5	9	80
93-14	60	70	18754	333	332	0.15	11	1170	7	4	46	7	1406	108.6	38	6	4	10	130
93-14	70	80	18755	281	35	0.06	9	950	16	7	63	6	898	72.0	55	4	3	7	75
93-14	80	90	18756	192	81	0.04	17	1250	12	7	48	5	876	44.4	37	3	3	5	49
93-14	90	100	18757	238	56	0.05	14	1410	12	6	60	6	909	52.3	37	3	2	6	79
93-14	100	110	18758	145	21	0.06	12	780	12	4	36	6	1315	76.4	37	4	3	7	82
93-14	110	120	18759	205	66	0.05	23	690	6	7	40	6	1631	103.6	44	6	3	7	57
93-14	120	130	18760	212	59	0.05	25	540	11	6	40	6	901	71.2	39	4	3	6	73
93-14	130	140	18761	242	104	0.05	28	530	10	8	40	5	625	65.2	43	4	2	7	75
93-14	140	150	18762	273	125	0.05	24	460	14	8	37	6	913	61.9	40	3	3	7	100
93-14	150	160	18763	217	57	0.07	16	530	9	7	41	5	971	60.6	36	4	3	5	67
93-14	160	170	18764	282	46	0.07	12	420	20	5	48	6	1208	66.2	36	4	3	7	69
93-14	170	180	18765	265	63	0.10	8	610	10	4	95	8	1340	80.7	39	6	3	7	76
93-14	180	190	18766	290	67	0.17	9	470	9	3	84	9	1880	100.3	37	7	4	7	57
93-14	190	200	18767	324	80	0.17	6	500	6	4	140	8	1790	122.7	37	7	4	10	79
93-14	200	210	18768	400	76	0.10	5	570	13	4	62	6	1573	112.6	44	6	4	9	70
93-14	210	220	18769	344	114	0.09	5	860	12	7	39	6	1419	113.6	43	5	3	8	70
93-14	220	230	18770	361	357	0.10	1	610	12	5	45	6	2184	154.4	42	7	5	10	81
93-14	230	240	18771	352	19	0.10	5	430	8	6	41	7	1793	208.5	45	8	4	12	84
93-14	240	250	18772	220	39	0.22	9	680	7	3	52	6	1248	129.9	38	6	3	8	76
93-14	250	260	18773	632	27	0.34	101	1270	15	4	191	13	1741	138.4	58	7	5	9	105
93-14	260	270	18774	309	25	0.11	23	1650	10	7	66	8	1319	132.0	44	6	4	8	68
93-14	270	280	18775	236	46	0.07	15	1160	5	3	41	5	1522	93.6	34	4	4	7	79
93-14	280	290	18776	241	15	0.10	4	850	4	2	31	5	1815	78.3	25	4	3	7	91
93-14	290	300	18777	335	18	0.19	4	620	10	4	41	7	2594	136.3	34	7	5	9	70
93-14	300	310	18778	314	76	0.11	5	290	5	4	53	6	2495	85.6	31	6	4	8	87
93-14	310	320	18779	317	27	0.13	6	520	6	2	72	6	2336	80.8	31	7	4	7	59
93-14	320	330	18780	420	45	0.24	1	940	8	1	63	6	3004	124.6	33	7	4	9	73
93-14	330	340	18781	394	31	0.27	1	930	2	1	69	8	2581	121.2	31	8	5	8	68
93-14	340	350	18782	586	21	0.30	1	690	1	2	88	7	3051	155.0	41	9	5	11	69
93-14	350	360	18783	423	86	0.22	2	610	6	1	56	7	2781	123.0	36	8	5	9	73
93-14	360	370	18784	396	56	0.12	7	920	4	3	63	5	2263	117.8	40	6	4	12	76
93-14	370	380	18785	445	17	0.18	1	450	6	1	113	5	2193	115.3	34	6	4	9	94
93-14	380	390	18786	356	31	0.16	1	480	4	1	68	6	2925	135.7	34	7	4	8	69
93-14	390	400	18787	341	41	0.14	4	500	5	2	91	6	2357	92.3	32	6	4	7	69

II - 213

MIN-EN LABORATORIES

705 W. 15th St.

North Vancouver, B.C.

Phone: 980-5814

Huckleberry

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)		SAMPLE	Cu-ASSAY	AG	AL	AS	B	BA	BE	BI	CA	CD	CO	CU	FE	K	LI	MG
HOLE#	START	END	NAME	%	PPM	%	PPM	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	%	%	PPM	%
93-15	65	70	17851	0.256	1.6	1.99	1	7	210	0.3	3	2.00	0.1	16	2341	3.75	0.79	12	1.62
93-15	70	80	17852	0.565	3.5	2.24	1	8	470	0.1	1	1.98	0.1	20	5152	4.58	0.85	13	1.66
93-15	80	90	17853	0.338	2.3	2.60	1	8	367	0.2	5	1.98	0.1	18	3105	4.62	0.74	11	1.55
93-15	90	100	17854	0.324	2.3	2.13	1	7	389	0.3	5	1.78	0.1	18	2949	4.78	0.58	9	1.16
93-15	100	110	17855	0.434	2.8	2.15	1	6	508	0.2	3	1.73	0.1	19	3959	4.88	0.73	10	1.37
93-15	110	120	17856	0.415	2.6	1.86	1	7	273	0.2	2	1.97	0.1	17	3846	4.31	0.64	11	1.38
93-15	120	130	17857	0.722	4.2	1.44	1	6	481	0.1	1	1.68	0.1	19	6683	4.13	0.83	12	1.56
93-15	130	140	17858	0.601	2.9	1.25	1	5	262	0.1	1	1.74	0.1	15	5133	3.57	0.54	11	1.33
93-15	140	150	17859	0.307	2.0	1.35	1	5	445	0.1	4	1.41	0.1	18	2841	4.56	0.70	11	1.32
93-15	150	160	17860	0.343	1.5	1.10	1	5	297	0.1	1	1.63	0.1	12	3264	2.93	0.55	12	1.25
93-15	160	170	17861	0.122	0.7	0.61	1	3	188	0.2	1	1.50	0.1	5	1029	1.37	0.26	5	0.43
93-15	170	180	17862	0.171	1.4	1.21	28	5	632	0.3	1	2.45	0.1	7	1459	1.39	0.35	11	0.68
93-15	180	190	17863	0.106	1.5	1.36	6	5	550	0.3	1	3.64	0.1	12	910	2.00	0.19	5	0.64
93-15	190	200	17864	0.157	1.4	0.38	23	4	354	0.1	1	2.46	0.1	2	1249	0.57	0.21	2	0.08
93-15	200	210	17865	0.121	1.0	0.28	10	3	309	0.1	1	2.36	0.1	1	967	0.29	0.21	1	0.03
93-15	210	220	17866	0.096	1.1	0.24	13	4	303	0.1	1	2.60	0.1	1	749	0.22	0.18	1	0.02
93-15	220	230	17867	0.102	1.0	0.24	14	4	368	0.1	1	2.47	0.1	1	813	0.26	0.16	1	0.04
93-15	230	240	17868	0.151	1.4	0.32	26	4	583	0.1	1	2.54	0.1	1	1259	0.35	0.22	1	0.05
93-15	240	250	17869	0.104	1.2	0.30	1	4	242	0.2	1	2.06	0.1	2	837	0.50	0.21	1	0.18
93-15	250	260	17870	0.304	1.5	0.76	1	3	351	0.2	1	1.95	0.1	8	2660	2.09	0.47	8	0.81
93-15	260	270	17871	0.478	1.7	0.82	1	3	226	0.2	1	1.89	0.1	11	4224	3.17	0.46	7	0.87
93-15	270	280	17872	0.550	2.1	1.14	1	5	402	0.3	1	2.10	0.1	12	5081	3.39	0.47	9	0.84
93-15	280	290	17873	0.254	1.0	0.75	1	4	297	0.2	1	1.90	0.1	7	2261	2.10	0.22	8	0.65
93-15	290	300	17874	0.300	1.2	1.01	1	4	243	0.2	1	2.38	0.1	9	2707	2.43	0.25	9	0.92
93-15	300	310	17875	0.305	0.9	1.05	1	4	209	0.3	1	1.90	0.1	12	2637	4.02	0.26	8	0.94
93-15	310	320	17876	0.312	1.2	1.17	1	4	352	0.3	1	1.97	0.1	12	2728	3.52	0.40	6	0.77
93-15	320	330	17877	0.267	1.0	1.22	1	5	189	0.4	1	2.26	0.1	8	2129	2.55	0.27	5	0.66
93-15	330	340	17878	0.191	0.9	0.98	1	5	345	0.3	1	3.17	0.1	5	1610	1.53	0.24	7	0.38
93-15	340	350	17879	0.137	0.8	0.59	4	5	420	0.3	1	2.67	0.1	3	1155	0.94	0.22	3	0.22
93-15	350	360	17880	0.155	0.8	1.15	1	5	472	0.3	1	2.92	0.1	5	1321	1.29	0.17	6	0.60
93-15	360	370	17881	0.181	0.7	1.84	1	6	205	0.5	1	2.02	0.1	8	1612	2.11	0.09	10	1.29
93-15	370	380	17882	0.212	0.8	1.71	1	6	304	0.5	1	2.01	0.1	8	1817	2.13	0.08	12	1.29
93-15	380	390	17883	0.183	1.4	2.26	8	7	557	0.5	1	2.87	0.1	6	1666	1.42	0.07	9	1.31

II-222

MIN-EN LABORATORIES
 705 W. 15th St.
 North Vancouver, B.C. Huckleberry
 Phone: 980-5814

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)		SAMPLE	MN	MO	NA	NI	P	PB	SB	SR	TH	TI	V	ZN	GA	SN	W	CR
HOLE#	START	END	NAME	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM
93-15	65	70	17851	317	212	0.12	4	270	5	3	38	10	1923	148.2	34	8	5	8	72
93-15	70	80	17852	352	166	0.15	1	720	11	7	49	11	2394	122.2	63	9	5	11	109
93-15	80	90	17853	347	60	0.26	1	900	11	5	64	12	2403	137.1	54	10	5	12	131
93-15	90	100	17854	339	30	0.23	1	840	6	4	50	10	2424	120.0	37	9	5	8	84
93-15	100	110	17855	377	57	0.20	1	960	14	6	54	9	2790	124.1	39	9	5	10	106
93-15	110	120	17856	320	179	0.19	1	940	10	5	45	10	2507	121.7	38	9	5	9	102
93-15	120	130	17857	299	113	0.09	2	910	16	8	30	9	2962	121.0	58	8	6	11	109
93-15	130	140	17858	290	51	0.07	3	1190	24	7	32	8	1909	130.5	90	7	4	8	76
93-15	140	150	17859	270	61	0.09	1	810	8	3	25	8	2591	152.6	38	8	5	9	107
93-15	150	160	17860	276	96	0.05	5	530	7	3	27	6	1581	125.1	34	6	3	8	79
93-15	160	170	17861	329	44	0.04	3	310	6	1	16	3	345	35.5	18	2	2	5	78
93-15	170	180	17862	413	86	0.03	13	480	13	2	33	6	390	39.5	30	3	2	3	58
93-15	180	190	17863	758	112	0.02	37	630	16	2	42	6	381	41.8	32	4	3	5	87
93-15	190	200	17864	395	201	0.04	2	290	24	5	26	4	11	6.4	19	1	1	4	88
93-15	200	210	17865	382	168	0.04	3	240	15	5	41	3	7	3.7	15	1	1	3	71
93-15	210	220	17866	489	182	0.04	1	140	18	6	50	3	6	3.5	33	1	1	3	58
93-15	220	230	17867	648	287	0.04	1	140	28	6	50	3	6	3.7	42	1	1	2	47
93-15	230	240	17868	545	269	0.04	2	150	54	7	54	3	8	4.3	141	1	1	3	57
93-15	240	250	17869	383	232	0.04	3	290	11	2	40	2	38	9.5	15	1	1	4	63
93-15	250	260	17870	308	136	0.04	2	430	8	3	35	4	804	70.5	32	4	3	5	61
93-15	260	270	17871	270	121	0.04	4	650	9	5	34	6	1040	112.9	33	5	3	6	69
93-15	270	280	17872	335	199	0.04	4	670	9	7	36	6	941	148.4	45	6	4	8	90
93-15	280	290	17873	279	180	0.04	5	370	10	3	21	5	379	65.1	29	4	2	5	75
93-15	290	300	17874	316	82	0.06	6	730	12	4	31	7	623	97.7	39	5	3	6	89
93-15	300	310	17875	379	36	0.04	3	440	26	4	23	6	871	164.5	66	6	4	8	64
93-15	310	320	17876	299	111	0.05	2	420	3	3	22	5	1086	108.2	41	5	4	8	97
93-15	320	330	17877	302	145	0.04	4	560	5	3	29	6	555	84.5	35	5	2	6	71
93-15	330	340	17878	436	85	0.03	3	320	23	2	35	4	111	30.5	145	2	2	4	78
93-15	340	350	17879	275	232	0.03	2	210	11	1	36	3	60	17.7	25	2	1	4	88
93-15	350	360	17880	384	168	0.04	3	400	8	2	39	6	193	43.5	25	3	2	3	48
93-15	360	370	17881	345	48	0.06	8	990	12	1	39	9	444	91.7	38	5	3	8	110
93-15	370	380	17882	373	46	0.05	9	850	16	2	61	9	294	60.3	34	5	3	4	63
93-15	380	390	17883	398	55	0.08	9	1170	14	2	239	10	384	59.1	31	6	2	6	67

11-22-77

MIN-EN LABORATORIES

705 W. 15th St.

North Vancouver, B.C.

Phone: 980-5814

Huckleberry

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)		SAMPLE	Cu-ASSAY	AG	AL	AS	B	BA	BE	BI	CA	CD	CO	CU	FE	K	LI	MG
HOLE#	START	END	NAME	%	PPM	%	PPM	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	%	%	PPM	%
93-16	60	70	17551	0.396	2.0	1.00	1	5	197	0.1	1	1.24	0.1	11	3463	2.91	0.27	10	0.76
93-16	70	80	17552	0.670	3.6	0.78	1	3	231	0.1	1	1.53	0.1	14	5943	2.57	0.25	10	0.49
93-16	80	90	17553	0.417	2.7	1.80	1	6	230	0.2	1	1.87	0.1	17	3797	3.49	0.62	14	1.30
93-16	90	100	17554	0.452	2.9	1.42	1	6	190	0.2	1	1.61	0.1	17	4215	3.60	0.58	14	1.17
93-16	100	110	17555	0.443	3.1	1.77	1	6	182	0.1	1	1.66	0.1	24	4021	3.56	0.65	15	1.35
93-16	110	120	17556	0.731	4.1	1.62	1	5	270	0.1	1	1.62	0.1	41	6306	3.83	0.72	16	1.66
93-16	120	130	17557	0.756	4.7	1.56	1	5	299	0.1	1	1.47	0.1	29	6702	3.40	0.85	16	1.61
93-16	130	140	17558	0.410	2.8	1.37	1	5	240	0.1	1	1.84	0.1	25	3888	3.57	0.71	15	1.37
93-16	140	150	17559	0.326	2.4	1.50	1	5	332	0.1	1	1.46	0.1	35	3010	3.74	0.81	16	1.38
93-16	150	160	17560	0.745	4.2	1.45	1	5	233	0.1	1	1.68	0.1	35	6593	3.78	0.64	15	1.43
93-16	160	170	17561	0.482	3.0	1.46	1	5	313	0.1	1	1.68	0.1	40	4207	3.56	0.65	14	1.35
93-16	170	180	17562	0.349	2.1	1.69	1	4	504	0.2	1	2.06	0.1	17	3078	2.62	0.70	15	1.45
93-16	180	190	17563	0.649	3.2	1.14	1	4	365	0.1	1	2.13	0.1	23	5433	2.60	0.45	11	0.89
93-16	190	200	17564	0.548	2.7	0.86	1	2	303	0.1	1	1.66	0.1	21	4541	2.32	0.31	8	0.68
93-16	200	210	17565	0.549	3.0	1.43	72	4	545	1.6	1	2.19	0.1	26	4391	0.97	0.92	16	1.32
93-16	210	220	17566	0.307	3.3	1.69	43	6	727	0.2	2	2.71	0.1	31	2748	4.10	0.81	15	1.48
93-16	220	230	17567	0.460	3.3	1.58	1	5	487	0.1	1	2.05	0.1	29	4135	3.45	0.78	13	1.40
93-16	230	240	17568	0.663	4.0	1.32	1	5	361	0.2	1	2.49	0.1	28	5579	3.54	0.52	12	1.21
93-16	240	250	17569	0.326	2.5	1.08	1	4	186	0.2	1	2.04	0.1	30	2799	3.23	0.36	12	1.11
93-16	250	260	17570	0.644	3.7	1.09	1	4	127	0.2	1	1.90	0.1	47	5395	3.84	0.32	12	1.12
93-16	260	270	17571	1.023	5.6	1.40	1	5	243	0.1	1	1.57	0.1	34	8513	4.26	0.63	13	1.40
93-16	270	280	17572	0.682	4.1	1.34	1	5	246	0.2	1	2.12	0.1	37	5873	3.41	0.61	13	1.40
93-16	280	290	17573	0.761	4.5	2.96	1	9	451	0.2	1	2.27	0.1	31	6354	4.99	1.36	21	2.78
93-16	290	300	17574	0.494	3.4	2.09	1	7	677	0.2	1	1.50	0.1	31	4193	4.56	1.17	18	1.84
93-16	300	310	17575	0.248	2.2	1.50	1	4	476	0.3	4	1.18	0.1	33	2081	3.49	0.85	16	1.46
93-16	310	320	17576	0.363	2.7	1.33	1	4	166	0.2	1	1.81	0.1	32	3042	3.74	0.47	14	1.28
93-16	320	330	17577	0.403	2.9	1.10	1	4	133	0.2	1	1.94	0.1	30	3648	3.43	0.34	11	0.99
93-16	330	340	17578	0.422	2.9	1.67	1	5	433	0.3	1	1.49	0.1	30	3724	4.96	0.89	18	1.52
93-16	340	350	17579	0.461	3.1	1.96	1	6	469	0.2	1	1.51	0.1	36	3728	4.34	0.81	14	1.51
93-16	350	360	17580	0.962	5.0	1.62	1	5	388	0.2	1	1.71	0.1	25	7982	3.86	0.80	14	1.53
93-16	360	370	17581	0.170	1.7	4.51	11	12	367	0.3	7	3.24	0.1	17	1553	3.88	0.99	15	2.34
93-16	370	380	17582	0.282	2.1	3.03	1	9	303	0.3	4	2.83	0.1	16	2361	3.00	1.04	19	2.72
93-16	380	390	17583	0.352	2.6	2.36	1	7	459	0.2	1	1.96	0.1	19	3062	3.18	0.69	14	1.42
93-16	390	400	17584	0.244	2.1	1.61	1	5	424	0.3	1	1.94	0.1	17	2205	2.79	0.46	12	1.25

93-16 - 11

MIN-EN LABORATORIES

705 W. 15th St.

North Vancouver, B.C.

Phone: (604) 271-1111

Huckleberry

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)		SAMPLE	MN	MO	NA	NI	P	PB	SB	SR	TH	TI	V	ZN	GA	SN	W	CR
HOLE#	START	END	NAME	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM
93-16	60	70	17551	460	17	0.04	6	880	10	6	26	3	636	65.4	32	3	2	4	58
93-16	70	80	17552	447	65	0.03	4	780	14	10	29	3	380	44.8	26	2	1	7	116
93-16	80	90	17553	398	58	0.14	1	880	10	6	48	9	1391	84.6	28	6	3	7	83
93-16	90	100	17554	408	46	0.08	1	870	8	5	40	6	1402	79.8	31	6	3	6	87
93-16	100	110	17555	374	46	0.14	2	980	113	5	48	7	1654	81.0	69	6	3	8	100
93-16	110	120	17556	381	24	0.07	1	950	11	8	38	8	1789	102.9	36	7	3	8	77
93-16	120	130	17557	334	82	0.07	3	880	8	8	34	7	1505	92.9	37	6	3	7	76
93-16	130	140	17558	351	69	0.05	1	1460	13	5	42	7	1439	91.1	35	6	3	6	77
93-16	140	150	17559	312	17	0.07	1	620	7	4	33	6	1540	85.2	28	7	4	5	64
93-16	150	160	17560	402	48	0.04	1	810	2	9	38	9	1291	76.8	34	6	4	5	57
93-16	160	170	17561	377	33	0.05	1	740	2	5	37	9	1101	69.7	28	5	3	5	52
93-16	170	180	17562	325	68	0.06	2	770	4	4	58	7	1015	82.4	25	6	3	4	57
93-16	180	190	17563	354	42	0.04	4	740	7	7	51	5	451	41.6	27	3	2	3	45
93-16	190	200	17564	304	143	0.03	6	560	11	7	42	5	480	49.8	23	3	3	4	65
93-16	200	210	17565	459	23	0.06	15	700	64	20	60	29	1269	86.3	116	11	10	9	81
93-16	210	220	17566	586	21	0.05	2	720	48	12	55	12	1629	105.9	131	8	4	8	84
93-16	220	230	17567	317	93	0.06	4	1230	6	8	48	11	1487	92.8	29	7	4	8	67
93-16	230	240	17568	322	60	0.05	4	800	11	10	67	11	1274	81.7	32	6	3	8	87
93-16	240	250	17569	277	27	0.04	5	950	8	6	47	11	1107	93.3	29	6	3	7	70
93-16	250	260	17570	325	26	0.03	9	690	11	10	40	9	1045	82.8	34	5	3	8	80
93-16	260	270	17571	306	7	0.05	9	890	10	14	35	10	1919	123.0	34	7	4	10	79
93-16	270	280	17572	297	53	0.05	7	1010	12	10	52	10	1724	102.5	31	7	4	8	67
93-16	280	290	17573	436	23	0.16	17	670	7	11	59	16	2209	243.6	39	10	5	11	74
93-16	290	300	17574	386	26	0.07	2	840	7	8	36	10	2527	131.4	30	9	4	10	69
93-16	300	310	17575	313	15	0.06	1	610	5	4	26	9	1853	86.5	24	7	4	7	60
93-16	310	320	17576	369	13	0.05	1	1460	3	7	44	10	1303	68.7	30	6	3	7	68
93-16	320	330	17577	354	67	0.04	3	690	8	7	42	10	876	65.6	30	6	3	7	88
93-16	330	340	17578	399	37	0.04	1	630	8	6	32	11	1959	126.8	31	8	5	8	66
93-16	340	350	17579	373	12	0.11	4	640	11	7	49	11	1857	117.0	30	8	4	8	78
93-16	350	360	17580	291	8	0.08	5	730	15	13	44	10	1530	103.4	36	8	3	9	77
93-16	360	370	17581	304	6	0.45	20	650	9	7	144	17	1502	226.8	24	12	4	17	204
93-16	370	380	17582	331	157	0.25	17	550	10	6	101	14	1447	199.1	30	10	4	14	159
93-16	380	390	17583	296	14	0.23	3	800	11	7	60	11	1192	77.2	26	8	3	8	97
93-16	390	400	17584	313	102	0.11	4	880	6	6	56	10	1114	75.7	26	6	3	6	73

1A2-11

MIN-EN LABORATORIES
 705 W. 15th St.
 North Vancouver, B.C.
 Phone: 980-5814

Huckleberry

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)		SAMPLE	Cu-ASSAY	AG	AL	AS	B	BA	BE	BI	CA	CD	CO	CU	FE	K	LI	MG
HOLE#	START	END	NAME	%	PPM	%	PPM	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	%	%	PPM	%
93-17	60	70	18851	0.587	3.1	1.69	1	6	507	0.2	1	1.11	0.1	20	5356	4.76	0.95	13	1.65
93-17	70	80	18852	0.386	2.7	2.09	1	8	1866	0.3	6	1.49	0.1	22	3533	4.58	0.84	14	2.07
93-17	80	90	18853	0.395	3.3	2.16	1	9	3011	0.3	8	1.49	0.1	24	3868	4.40	0.81	14	2.23
93-17	90	100	18854	0.262	1.5	1.06	1	6	396	0.4	1	1.80	0.1	7	2451	2.04	0.24	6	0.69
93-17	100	110	18855	0.299	1.6	0.85	6	5	268	0.4	1	2.21	0.1	5	2625	1.70	0.18	5	0.39
93-17	110	120	18856	0.412	2.4	1.62	1	7	498	0.4	1	1.63	0.1	16	3798	3.30	0.85	12	1.48
93-17	120	130	18857	0.397	2.7	1.01	148	8	237	0.4	1	2.69	0.1	11	3438	2.14	0.26	8	0.35
93-17	130	140	18858	0.635	3.3	1.52	3	7	454	0.5	1	2.61	0.1	12	5722	3.44	0.46	9	0.78
93-17	140	150	18859	0.737	3.7	1.47	36	8	784	0.3	1	1.81	0.1	15	7015	3.58	0.55	11	1.24
93-17	150	160	18860	0.681	3.0	1.21	9	7	587	0.3	1	1.73	0.1	12	6320	2.95	0.42	11	0.98
93-17	160	170	18861	0.610	2.1	1.00	7	6	264	0.4	1	1.23	0.1	8	5731	2.27	0.19	9	0.77
93-17	170	180	18862	0.831	3.4	1.02	77	6	146	0.3	1	2.13	0.1	8	7820	2.13	0.18	11	0.62
93-17	180	190	18863	0.617	2.6	1.03	4	7	151	0.3	1	2.18	0.1	7	5486	1.69	0.13	6	0.55
93-17	190	200	18864	0.812	3.9	1.93	2	10	64	0.5	1	2.91	0.1	10	7806	2.43	0.18	9	1.30
93-17	200	210	18865	0.360	2.0	2.18	9	9	496	0.6	1	2.56	0.1	12	3533	2.39	0.25	8	0.97
93-17	210	220	18866	0.248	2.2	1.25	6	7	525	0.5	1	3.71	0.1	11	2259	2.49	0.25	8	0.81
93-17	220	228	18867	0.194	1.8	1.08	2	6	352	0.3	5	1.13	0.1	13	1627	2.47	0.30	10	1.20

II-243

MIN-EN LABORATORIES
 705 W. 15th St.
 North Vancouver, B.C.
 Phone: 980-5814 Huckleberry

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)		SAMPLE	MN	MO	NA	NI	P	PB	SB	SR	TH	TI	V	ZN	GA	SN	W	CR
HOLE#	START	END	NAME	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM
93-17	60	70	18851	292	23	0.05	2	680	6	7	15	11	2489	172.8	36	9	6	12	88
93-17	70	80	18852	404	198	0.10	34	1230	1	4	42	15	2973	165.2	59	10	6	12	145
93-17	80	90	18853	402	114	0.07	35	1400	2	6	47	15	3567	154.8	67	10	6	13	147
93-17	90	100	18854	286	104	0.03	7	440	4	4	16	7	394	40.1	33	4	2	5	67
93-17	100	110	18855	315	142	0.03	2	300	6	5	15	6	123	23.4	27	3	2	6	105
93-17	110	120	18856	341	129	0.04	2	460	3	7	15	9	2061	106.0	32	7	4	8	66
93-17	120	130	18857	508	609	0.01	4	640	65	33	18	8	273	31.7	264	4	3	5	83
93-17	130	140	18858	322	64	0.02	4	950	11	11	23	10	1031	60.6	39	6	4	7	75
93-17	140	150	18859	258	262	0.04	9	1000	14	12	25	12	1417	77.8	42	8	4	11	142
93-17	150	160	18860	241	199	0.04	7	830	9	10	22	8	1017	61.2	35	5	3	7	91
93-17	160	170	18861	191	111	0.06	8	470	4	9	15	7	278	34.1	34	3	2	10	162
93-17	170	180	18862	167	191	0.02	5	580	16	14	15	7	203	29.8	49	4	2	6	81
93-17	180	190	18863	186	219	0.04	5	410	11	9	18	7	68	24.6	30	3	2	6	80
93-17	190	200	18864	327	499	0.04	10	440	19	13	31	11	195	60.0	31	6	4	7	80
93-17	200	210	18865	249	181	0.05	8	1040	11	7	39	13	305	65.1	30	6	3	7	81
93-17	210	220	18866	478	142	0.04	9	940	9	6	50	12	457	56.1	39	6	3	7	89
93-17	220	228	18867	278	57	0.06	8	920	7	3	60	10	1428	69.1	36	6	3	7	96

612-II

MIN-EN LABORATORIES
 707 W. 15th St.
 North Vancouver, B.C.
 Phone: 980-5814

I.C.P. and Copper assay

New Canamin Resources

Huckleberry

HOLE#	INTERVAL(feet)	SAMPLE	Cu-ASSAY	AG	AL	AS	B	BA	BE	BI	CA	CD	CO	CU	FE	K	LI	MG	
HOLE#	START	END	NAME	%	PPM	%	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	%	%	PPM	%	
93-18	46	50	18951	0.612	3.4	1.45	1	5	179	0.2	1	1.39	0.1	19	5826	5.47	0.59	10	1.27
93-18	50	60	18952	0.610	3.5	1.14	1	5	113	0.2	1	1.21	0.1	18	5654	5.11	0.34	8	1.03
93-18	60	70	18953	0.582	2.7	1.29	3	4	127	0.2	1	1.18	0.1	17	5220	4.90	0.40	7	1.19
93-18	70	80	18954	0.471	1.9	1.11	1	3	119	0.2	1	1.16	0.1	14	4174	4.34	0.41	7	1.04
93-18	80	90	18955	0.316	1.9	1.13	1	3	128	0.3	3	1.29	0.1	16	2854	4.79	0.37	7	1.01
93-18	90	100	18956	0.540	2.8	1.11	1	4	167	0.2	1	0.92	0.1	18	5136	5.35	0.39	8	1.11
93-18	100	110	18957	0.987	3.9	0.88	1	4	98	0.1	1	1.25	0.1	16	8490	4.09	0.27	7	0.88
93-18	110	120	18958	0.681	3.4	0.88	1	4	73	0.3	1	1.02	0.1	27	6624	4.67	0.18	7	0.85
93-18	120	130	18959	0.667	3.5	1.41	1	5	652	0.1	1	0.86	0.1	21	6513	4.68	0.75	10	1.35
93-18	130	140	18960	0.449	2.2	1.94	1	5	679	0.1	7	1.10	0.1	26	4282	7.24	1.21	12	1.99
93-18	140	150	18961	0.491	2.3	2.51	1	5	314	0.4	1	2.03	0.1	19	4211	4.51	1.01	13	2.35
93-18	150	160	18962	0.458	2.1	1.67	1	6	689	0.2	1	1.10	0.1	19	4048	4.86	0.96	11	1.59
93-18	160	170	18963	0.525	2.3	1.62	1	5	573	0.2	1	1.25	0.1	19	4470	4.90	0.92	12	1.57
93-18	170	180	18964	0.776	2.9	1.46	1	7	370	0.1	1	1.10	0.1	20	6568	4.25	0.76	10	1.45
93-18	180	190	18965	0.572	2.0	1.06	1	6	214	0.3	1	1.25	0.1	9	5149	2.20	0.13	6	0.56
93-18	190	200	18966	0.301	1.2	0.78	1	3	265	0.2	1	1.41	0.1	6	2600	1.60	0.15	6	0.47
93-18	200	210	18967	0.244	1.1	0.78	1	3	292	0.2	1	1.37	0.1	5	2055	1.56	0.12	5	0.49
93-18	210	220	18968	0.220	1.3	0.87	1	4	120	0.3	1	2.35	0.1	7	1797	1.85	0.18	6	0.53
93-18	220	230	18969	0.335	2.2	0.72	2	4	76	0.3	1	1.86	0.1	5	2575	1.56	0.12	6	0.56
93-18	230	240	18970	0.169	0.7	0.70	3	3	247	0.3	1	1.45	0.1	5	1456	1.55	0.12	7	0.53
93-18	240	250	18971	0.128	0.8	0.80	1	3	465	0.3	1	1.84	0.1	6	1086	1.60	0.16	6	0.52
93-18	250	260	18972	0.394	2.0	0.67	3	4	66	0.2	1	1.70	0.1	4	3234	1.23	0.16	4	0.44
93-18	260	270	18973	0.511	2.1	0.63	7	4	153	0.2	1	2.02	0.1	5	4582	1.39	0.18	3	0.30
93-18	270	280	18974	0.206	1.0	0.79	2	3	172	0.3	1	1.40	0.1	5	1798	1.61	0.10	6	0.56
93-18	280	290	18975	0.187	1.1	0.96	1	2	126	0.3	2	1.15	0.1	7	1685	1.85	0.10	8	0.67
93-18	290	300	18976	0.214	1.2	0.62	3	3	125	0.2	1	2.23	0.1	8	1795	1.43	0.14	4	0.38
93-18	300	310	18977	0.347	1.6	0.61	9	3	258	0.2	1	2.25	0.1	5	2852	1.46	0.15	3	0.28
93-18	310	320	18978	0.698	2.8	1.37	1	4	389	0.3	1	2.40	0.1	11	5915	2.52	0.43	5	0.87
93-18	320	330	18979	0.504	2.2	3.03	1	8	363	0.4	1	1.65	0.1	19	4215	4.61	1.05	15	2.45
93-18	330	340	18980	0.315	1.6	1.65	1	4	156	0.3	1	1.62	0.1	11	2808	2.52	0.45	9	1.15
93-18	340	350	18981	0.378	1.5	1.53	1	6	231	0.3	1	1.64	0.1	10	2905	2.35	0.33	7	0.94
93-18	350	360	18982	0.237	1.4	1.41	1	5	156	0.3	3	1.39	0.1	12	2089	2.59	0.38	11	1.31
93-18	360	370	18983	0.194	1.2	1.45	1	4	311	0.3	3	1.93	0.1	11	1554	2.52	0.48	10	1.34
93-18	370	380	18984	0.236	1.5	1.49	1	4	382	0.2	1	1.73	0.1	11	1952	2.45	0.57	12	1.39
93-18	380	390	18985	0.226	1.3	0.96	5	5	231	0.2	1	1.84	0.1	6	1840	1.21	0.21	5	0.58
93-18	390	400	18986	0.418	1.8	1.50	1	5	236	0.3	1	1.51	0.1	11	3399	2.86	0.41	10	1.16
93-18	400	410	18987	0.310	1.7	2.54	1	7	508	0.4	4	1.71	0.1	17	2489	3.90	0.63	11	1.73

II-252

MIN-EN LABORATORIES
 705 W. 15th St.
 North Vancouver, B.C.
 Phone: 980-5814

Huckleberry

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)		SAMPLE	MN	MO	NA	NI	P	PB	SB	SR	TH	TI	V	ZN	GA	SN	W	CR
HOLE#	START	END	NAME	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM
93-18	46	50	18951	360	108	0.08	1	1080	18	11	21	10	2306	67.2	43	8	5	8	85
93-18	50	60	18952	365	91	0.08	1	940	16	12	19	8	2184	61.0	40	8	5	8	84
93-18	60	70	18953	310	64	0.08	1	980	13	10	19	8	2424	64.5	40	8	5	9	95
93-18	70	80	18954	269	66	0.06	1	890	12	9	16	7	1432	52.2	35	6	4	6	74
93-18	80	90	18955	365	135	0.06	1	960	32	10	16	8	1618	58.1	42	7	5	6	81
93-18	90	100	18956	313	36	0.09	1	1000	16	11	17	9	2117	62.7	45	8	5	7	80
93-18	100	110	18957	250	297	0.07	1	1030	16	14	15	6	1207	45.1	42	6	4	6	71
93-18	110	120	18958	231	269	0.10	1	1060	18	15	17	7	1889	47.4	41	6	5	8	89
93-18	120	130	18959	190	102	0.13	3	920	13	13	22	9	2801	82.4	48	9	6	9	80
93-18	130	140	18960	320	122	0.08	1	660	8	9	20	14	3504	232.5	51	12	8	11	71
93-18	140	150	18961	422	117	0.12	14	580	10	8	29	14	1749	182.7	36	9	6	14	175
93-18	150	160	18962	248	232	0.07	5	480	7	8	14	8	2304	173.5	34	9	6	10	86
93-18	160	170	18963	297	121	0.06	1	450	8	7	15	9	2266	174.9	34	8	5	9	67
93-18	170	180	18964	259	762	0.05	5	460	9	10	13	10	2314	137.9	39	8	6	9	61
93-18	180	190	18965	237	219	0.11	6	400	14	9	17	5	338	28.0	32	3	3	5	83
93-18	190	200	18966	239	76	0.08	3	280	7	5	14	3	230	18.3	25	2	2	4	68
93-18	200	210	18967	230	54	0.08	3	260	9	5	17	5	271	18.3	27	2	2	4	67
93-18	210	220	18968	296	147	0.04	3	350	12	4	12	7	97	22.3	27	3	3	4	66
93-18	220	230	18969	250	109	0.03	2	350	11	6	12	6	97	21.3	30	2	2	3	60
93-18	230	240	18970	222	79	0.05	3	290	7	5	10	6	96	19.2	31	2	2	4	70
93-18	240	250	18971	272	80	0.05	3	290	9	5	15	6	157	21.6	26	3	2	4	74
93-18	250	260	18972	211	258	0.04	4	320	10	7	11	6	43	15.6	25	2	2	4	70
93-18	260	270	18973	219	210	0.04	4	340	10	9	13	5	46	14.0	24	2	2	5	87
93-18	270	280	18974	241	46	0.07	2	270	9	5	19	5	239	20.1	31	3	2	4	65
93-18	280	290	18975	243	31	0.10	1	290	8	5	27	6	589	25.3	31	3	3	5	69
93-18	290	300	18976	264	89	0.04	4	320	6	4	16	5	78	19.3	26	2	2	5	79
93-18	300	310	18977	240	92	0.04	6	310	11	6	16	5	81	18.5	28	1	2	4	82
93-18	310	320	18978	293	117	0.03	7	330	9	15	20	6	759	77.8	50	5	3	6	74
93-18	320	330	18979	438	94	0.12	20	570	8	7	45	12	2149	155.1	46	10	7	12	137
93-18	330	340	18980	247	122	0.06	5	480	9	6	25	8	721	64.3	36	5	4	7	75
93-18	340	350	18981	237	97	0.05	7	450	11	6	34	8	594	62.4	32	5	3	5	59
93-18	350	360	18982	275	84	0.07	4	430	7	4	16	8	1097	67.1	32	5	3	6	73
93-18	360	370	18983	336	38	0.05	3	430	9	3	22	8	869	64.1	48	5	3	5	54
93-18	370	380	18984	288	184	0.05	1	460	12	3	25	8	1008	69.2	31	6	3	5	63
93-18	380	390	18985	219	355	0.06	4	300	9	6	58	5	103	27.9	24	3	3	4	76
93-18	390	400	18986	301	169	0.07	7	450	8	9	53	8	631	73.8	35	5	3	5	61
93-18	400	410	18987	429	73	0.07	7	700	9	7	56	12	1690	131.7	35	8	5	8	62

II-257

MIN-EN LABORATORIES

705 W. 15th St.

North Vancouver, B.C. Huckleberry

Phone: 960-5814

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)	SAMPLE	Cu-ASSAY	AG	AL	AS	B	BA	BE	BI	CA	CD	CO	CU	FE	K	LI	MG	
HOLE#	START	END	NAME	%	PPM	%	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	%	%	PPM	%	
93-18	410	420	18988	0.584	3.0	2.70	1	7	393	0.4	1	2.79	0.1	15	4619	3.17	0.40	10	1.43

252-11

MIN-EN LABORATORIES

705 W. 15th St.

North Vancouver, B.C.

Phone: 980-5814

Huckleberry

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)		SAMPLE	MN	MO	NA	NI	P	PB	SB	SR	TH	TI	V	ZN	GA	SN	W	CR
HOLE#	START	END	NAME	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM
93-18	410	420	18988	426	102	0.12	9	610	16	10	54	12	838	99.8	36	7	4	6	55

II-25-3

MIN-EN LABORATORIES

705 W. 15th St.

North Vancouver, B.C.

Phone: 980-5814

Huckleberry

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)	SAMPLE	Cu-ASSAY	AG	AL	AS	B	BA	BE	BI	CA	CD	CO	CU	FE	K	LI	MG	
HOLE#	START	END	NAME	%	PPM	%	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	%	%	PPM	%	
93-19	35	40	18901	0.445	2.6	1.33	1	5	291	0.2	1	1.10	0.1	14	3876	2.75	0.44	8	1.16
93-19	40	50	18902	0.274	1.5	1.28	1	4	131	0.2	2	1.33	0.1	10	2477	2.19	0.25	9	1.07
93-19	50	60	18903	1.060	3.8	1.11	1	4	82	0.2	1	1.52	0.1	11	9133	2.87	0.16	7	0.93
93-19	60	70	18904	2.230	6.0	1.39	1	8	150	0.2	1	1.43	0.1	18	10000	3.87	0.25	7	1.00
93-19	70	80	18905	0.331	1.6	1.37	1	5	148	0.2	1	1.61	0.1	12	3011	2.79	0.24	6	0.94
93-19	80	90	18906	0.701	3.0	1.54	1	5	303	0.2	1	1.28	0.1	18	6417	3.12	0.63	10	1.45
93-19	90	100	18907	0.760	3.5	2.27	1	7	598	0.2	1	1.26	0.1	24	7013	4.28	0.94	10	2.11
93-19	100	110	18908	0.645	2.7	1.15	1	4	508	0.1	1	0.84	0.1	16	5358	2.92	0.47	6	1.08
93-19	110	120	18909	0.832	3.8	3.28	10	10	511	0.4	1	2.45	0.1	23	7403	4.39	0.92	14	2.64
93-19	120	130	18910	0.567	2.9	1.78	1	6	890	0.3	1	1.71	0.1	16	5642	3.01	0.77	10	1.52
93-19	130	140	18911	0.784	3.2	1.40	1	7	251	0.2	1	1.43	0.1	15	6840	2.63	0.49	9	1.34
93-19	140	150	18912	1.025	4.0	3.76	4	12	284	0.3	1	2.04	0.1	25	9268	4.19	0.68	9	2.24
93-19	150	160	18913	0.986	4.3	2.05	1	7	313	0.2	1	1.67	0.1	22	8942	3.64	0.62	10	1.57
93-19	160	170	18914	0.586	2.9	1.73	1	5	587	0.2	1	1.23	0.1	21	5328	3.78	0.81	11	1.53
93-19	170	180	18915	0.425	1.9	1.17	1	5	105	0.3	1	1.32	0.1	11	3951	1.88	0.23	9	0.99
93-19	180	190	18916	0.422	2.1	1.25	5	5	126	0.2	1	1.32	0.1	11	3785	1.84	0.24	9	1.07
93-19	190	200	18917	0.419	1.9	1.13	1	6	117	0.2	1	1.24	0.1	10	3731	1.71	0.16	8	1.02
93-19	200	210	18918	0.553	3.2	2.64	2	8	351	0.2	1	1.63	0.1	21	5328	3.30	0.88	13	2.41
93-19	210	220	18919	0.842	3.7	2.57	1	7	436	0.2	1	1.19	0.1	32	7405	4.95	0.96	12	2.34
93-19	220	230	18920	0.415	1.9	3.04	1	8	248	0.4	1	1.98	0.1	21	3791	5.36	0.66	11	2.00
93-19	230	240	18921	0.416	2.1	3.14	1	8	293	0.3	1	2.68	0.1	20	3678	5.22	0.53	10	1.73
93-19	240	250	18922	0.280	1.6	3.48	1	8	606	0.4	5	2.36	0.1	22	2671	5.79	0.73	11	1.85
93-19	250	260	18923	0.383	1.7	2.78	1	7	408	0.3	1	2.11	0.1	17	3503	4.69	0.53	10	1.29
93-19	260	270	18924	0.447	1.8	3.13	1	8	273	0.4	1	2.45	0.1	21	3834	5.47	0.48	9	1.62
93-19	270	280	18925	0.384	1.9	3.21	1	8	404	0.4	1	2.38	0.1	18	3584	4.50	0.59	11	1.74
93-19	280	290	18926	0.373	2.0	2.37	2	8	342	0.4	1	1.84	0.1	14	3651	3.23	0.38	11	1.27
93-19	290	300	18927	0.671	2.9	2.01	1	6	428	0.2	1	1.45	0.1	21	5995	3.68	0.59	11	1.61
93-19	300	310	18928	0.497	2.5	2.14	1	7	509	0.3	6	1.43	0.1	22	4333	4.25	0.60	10	1.37
93-19	310	320	18929	0.446	2.4	2.54	1	7	678	0.3	6	1.58	0.1	22	3943	5.01	0.83	10	1.65
93-19	320	330	18930	0.665	3.2	2.05	1	7	665	0.2	1	1.15	0.1	25	5992	5.48	0.83	12	1.64
93-19	330	340	18931	0.921	4.3	2.22	1	8	393	0.3	1	1.31	0.1	24	8073	4.03	0.69	14	2.03
93-19	340	350	18932	0.471	2.2	1.72	1	5	516	0.3	4	1.14	0.1	22	4131	4.31	0.75	13	1.64
93-19	350	360	18933	0.552	2.4	1.90	1	6	592	0.3	1	1.26	0.1	19	5017	3.99	0.54	13	1.52
93-19	360	370	18934	0.424	1.6	1.63	1	6	340	0.3	1	1.34	0.1	13	3693	2.39	0.50	11	1.44
93-19	370	380	18935	0.285	1.8	2.39	1	7	277	0.4	2	2.71	0.1	12	2432	2.67	0.51	9	1.32
93-19	380	390	18936	0.368	2.5	0.98	21	5	100	0.3	1	3.64	0.1	9	3157	1.42	0.25	4	0.34
93-19	390	400	18937	0.241	1.6	1.37	2	5	66	0.4	1	3.57	0.1	8	2237	1.80	0.16	6	0.34

I-257

MIN-EN LABORATORIES

705 W. 15th St.

North Vancouver, B.C.

Phone: 980-5814

Huckleberry

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)		SAMPLE	MN	MO	NA	NI	P	PB	SB	SR	TH	TI	V	ZN	GA	SN	W	CR
HOLE#	START	END	NAME	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM
93-19	35	40	18901	176	49	0.09	1	520	11	8	19	7	1632	74.2	31	5	3	6	64
93-19	40	50	18902	203	98	0.10	2	750	9	7	23	6	1140	48.8	28	4	3	8	123
93-19	50	60	18903	261	235	0.07	5	900	17	15	22	7	764	45.5	36	3	3	6	48
93-19	60	70	18904	207	578	0.06	14	1040	22	27	26	7	937	56.8	46	5	5	8	90
93-19	70	80	18905	217	168	0.12	1	620	11	7	24	7	1398	64.5	33	5	3	6	64
93-19	80	90	18906	223	125	0.09	4	800	11	10	23	7	1929	85.4	42	7	4	8	93
93-19	90	100	18907	290	112	0.13	22	630	13	12	32	11	2625	160.3	53	8	6	11	112
93-19	100	110	18908	148	143	0.10	6	460	12	10	25	6	2031	81.8	56	5	4	6	49
93-19	110	120	18909	399	95	0.17	28	1470	11	13	109	16	2204	164.9	55	10	6	15	201
93-19	120	130	18910	221	202	0.10	2	2890	13	9	44	10	1541	85.6	39	6	4	7	62
93-19	130	140	18911	183	407	0.07	4	910	14	11	35	8	1689	91.9	36	6	4	8	89
93-19	140	150	18912	337	379	0.41	25	720	21	16	146	14	1923	180.0	57	10	7	15	162
93-19	150	160	18913	395	238	0.15	10	840	19	20	35	10	1679	110.8	56	7	5	11	127
93-19	160	170	18914	247	100	0.07	1	500	12	8	15	8	2536	121.3	42	8	5	7	45
93-19	170	180	18915	185	87	0.08	2	590	9	8	16	6	1001	52.9	31	4	3	6	85
93-19	180	190	18916	194	55	0.08	2	760	13	7	18	7	1190	49.3	32	5	2	4	45
93-19	190	200	18917	193	449	0.08	5	660	16	9	31	7	980	43.3	36	5	2	5	51
93-19	200	210	18918	353	133	0.18	29	740	12	11	103	13	2186	120.1	47	9	5	11	139
93-19	210	220	18919	401	62	0.20	18	860	16	14	133	13	3072	211.3	62	11	6	13	97
93-19	220	230	18920	669	68	0.10	2	620	17	9	70	14	1813	185.2	54	10	6	10	69
93-19	230	240	18921	697	49	0.13	2	920	9	7	84	13	1594	168.7	44	10	6	10	56
93-19	240	250	18922	776	27	0.18	2	1240	13	8	211	15	1804	179.6	50	11	7	9	62
93-19	250	260	18923	513	86	0.17	1	360	9	8	104	11	942	141.8	43	8	5	8	81
93-19	260	270	18924	660	25	0.17	3	560	13	9	82	14	1347	194.1	47	10	7	10	68
93-19	270	280	18925	539	27	0.16	2	530	12	9	102	14	1536	153.0	39	9	6	8	69
93-19	280	290	18926	384	45	0.14	3	440	16	10	100	10	948	75.7	46	7	4	7	85
93-19	290	300	18927	319	40	0.11	5	690	11	11	47	10	2077	136.3	49	8	4	8	60
93-19	300	310	18928	274	34	0.18	3	890	18	10	70	10	2776	148.1	46	9	5	10	85
93-19	310	320	18929	374	44	0.20	2	870	14	11	77	12	2671	154.4	47	10	6	10	71
93-19	320	330	18930	324	83	0.13	9	780	18	13	76	11	2925	163.1	54	10	6	11	97
93-19	330	340	18931	347	35	0.13	15	670	20	15	51	10	2039	144.9	62	8	5	10	96
93-19	340	350	18932	367	26	0.09	10	680	19	10	30	11	2402	161.5	49	9	5	11	102
93-19	350	360	18933	381	63	0.09	8	490	17	11	30	12	1832	130.2	50	8	5	9	88
93-19	360	370	18934	343	32	0.12	13	480	15	8	27	9	782	78.6	39	5	3	7	96
93-19	370	380	18935	477	84	0.18	25	410	22	10	35	11	870	80.2	43	7	4	9	111
93-19	380	390	18936	539	114	0.04	7	520	40	29	27	5	110	23.7	88	3	2	4	65
93-19	390	400	18937	453	83	0.05	3	570	19	15	25	7	77	26.5	37	4	2	3	43

II - 255

MIN-EN LABORATORIES
 705 W. 15th St.
 North Vancouver, B.C.
 Phone: 980-5814

Huckleberry

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)	SAMPLE	Cu-ASSAY	AG	AL	AS	B	BA	BE	BI	CA	CD	CO	CU	FE	K	LI	MG	
HOLE#	START	END	NAME	%	PPM	%	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	%	%	PPM	%	
93-20	65	70	18801	0.638	3.9	1.57	1	5	356	0.1	1	1.17	0.1	17	5513	3.65	0.78	10	1.55
93-20	70	80	18802	0.786	4.5	1.99	1	6	393	0.1	1	0.90	0.1	21	7654	4.57	1.18	16	2.09
93-20	80	90	18803	0.588	2.9	2.03	1	7	621	0.1	1	0.86	0.1	22	5413	5.14	1.07	12	2.02
93-20	90	100	18804	0.649	3.2	1.94	1	7	495	0.1	1	1.01	0.1	22	5848	4.91	1.04	14	2.00
93-20	100	110	18805	0.542	3.4	2.20	1	7	612	0.1	1	1.19	0.1	23	5437	5.59	1.10	14	2.09
93-20	110	120	18806	0.603	3.7	2.50	1	9	637	0.1	1	1.00	0.1	22	5421	4.69	1.16	14	2.15
93-20	120	130	18807	0.419	2.6	2.99	1	8	663	0.1	1	1.26	0.1	20	3874	4.64	1.17	13	2.19
93-20	130	140	18808	0.522	2.8	1.67	1	5	418	0.1	1	1.25	0.1	15	4589	3.51	0.71	13	1.52
93-20	140	150	18809	0.570	2.9	3.02	1	9	353	0.1	1	2.30	0.1	22	5183	6.26	1.02	15	2.21
93-20	150	160	18810	0.722	2.1	1.45	1	5	298	0.1	1	1.57	0.1	23	6056	6.72	0.79	11	1.71
93-20	160	170	18811	0.617	3.3	0.91	1	4	118	0.1	1	1.77	0.1	14	5509	2.83	0.31	11	1.11
93-20	170	180	18812	0.641	2.2	1.81	1	5	324	0.1	1	1.99	0.1	21	5648	6.61	0.91	14	1.84
93-20	180	190	18813	1.020	5.1	1.70	20	7	340	0.1	1	2.74	0.1	20	8656	5.12	0.81	15	1.53
93-20	190	200	18814	0.589	2.3	1.38	1	4	265	0.1	1	2.13	0.1	14	5316	3.68	0.57	13	1.23
93-20	200	210	18815	0.241	1.1	0.76	1	4	433	0.2	1	1.68	0.1	7	1984	2.31	0.31	7	0.65
93-20	210	220	18816	0.614	2.5	1.50	1	5	406	0.2	1	1.93	0.1	14	5122	3.72	0.67	14	1.28
93-20	220	230	18817	0.502	2.7	1.84	1	5	488	0.1	1	1.61	0.1	17	4430	4.12	0.94	15	1.84
93-20	230	240	18818	0.591	2.8	1.18	1	6	246	0.1	1	1.94	0.1	13	5301	3.47	0.47	11	1.24
93-20	240	250	18819	0.433	1.9	0.82	1	7	416	0.1	1	1.61	0.1	8	3719	2.16	0.35	8	0.79
93-20	250	260	18820	0.372	1.9	0.75	1	7	439	0.2	1	2.21	0.1	7	3222	1.51	0.25	7	0.62
93-20	260	270	18821	0.541	2.2	0.76	1	3	122	0.1	1	1.74	0.1	8	4581	1.71	0.24	10	0.88
93-20	270	280	18822	0.370	1.9	0.87	1	4	309	0.2	1	2.01	0.1	8	3262	1.95	0.32	9	0.87
93-20	280	290	18823	0.292	1.4	0.96	1	3	303	0.1	1	1.18	0.1	11	2513	2.75	0.33	10	1.03
93-20	290	300	18824	0.333	1.8	1.04	1	4	380	0.1	1	1.54	0.1	11	2952	2.78	0.42	10	1.01
93-20	300	310	18825	0.268	1.9	0.73	8	6	838	0.2	1	2.81	0.1	5	2374	1.53	0.29	5	0.31
93-20	310	320	18826	0.199	1.3	0.60	1	4	263	0.3	1	1.16	0.1	6	1638	1.74	0.20	7	0.46
93-20	320	330	18827	0.347	2.1	0.93	1	6	174	0.1	1	1.41	0.1	10	3232	2.47	0.25	11	0.94
93-20	330	340	18828	0.389	2.9	1.13	3	6	157	0.2	1	1.50	0.1	12	3502	2.79	0.23	11	0.90
93-20	340	350	18829	0.250	1.9	0.83	7	4	126	0.2	1	1.64	0.1	8	2226	2.15	0.22	8	0.67
93-20	350	360	18830	0.184	1.8	0.66	12	6	211	0.2	1	2.74	0.1	7	1528	1.24	0.20	3	0.25
93-20	360	370	18831	0.163	1.5	0.42	12	5	103	0.1	1	2.11	0.1	2	1378	0.53	0.20	2	0.14
93-20	370	380	18832	0.331	2.1	0.96	7	6	108	0.3	1	1.77	0.1	7	2854	1.83	0.19	8	0.68
93-20	380	390	18833	0.221	1.7	0.92	9	5	103	0.2	1	1.57	0.1	7	1931	1.84	0.18	9	0.90
93-20	390	400	18834	0.653	3.3	1.01	1	5	114	0.3	1	2.13	0.1	14	5991	3.86	0.18	10	1.04
93-20	400	410	18835	0.550	3.2	0.95	2	7	50	0.3	1	2.14	0.1	10	4859	2.37	0.12	8	0.91
93-20	410	420	18836	0.358	2.5	1.79	8	7	87	0.4	1	2.13	0.1	9	3299	2.43	0.11	11	1.31
93-20	420	430	18837	0.301	2.6	1.89	13	10	116	0.5	1	2.78	0.1	7	2629	1.60	0.14	10	0.96

I-256

MIN-EN LABORATORIES
 705 W. 15th St.
 North Vancouver, B.C.
 Phone: 980-5814

Huckleberry

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)		SAMPLE	MN	MO	NA	NI	P	PB	SB	SR	TH	TI	V	ZN	GA	SN	W	CR
HOLE#	START	END	NAME	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM
93-20	65	70	18801	231	142	0.11	11	440	4	7	23	7	1685	124.9	37	6	4	7	74
93-20	70	80	18802	347	145	0.13	13	560	8	10	27	10	2211	164.1	45	8	5	10	119
93-20	80	90	18803	288	78	0.11	7	680	8	6	27	10	2864	185.8	47	8	4	11	100
93-20	90	100	18804	304	345	0.08	8	900	7	7	29	9	2623	152.2	44	9	5	10	97
93-20	100	110	18805	336	117	0.16	3	1000	3	8	35	12	2927	158.5	45	9	5	11	89
93-20	110	120	18806	292	295	0.19	6	940	4	7	33	10	2892	140.4	49	9	5	9	73
93-20	120	130	18807	291	49	0.26	6	990	6	6	43	11	2835	157.2	39	9	5	11	112
93-20	130	140	18808	276	133	0.13	3	1030	6	6	31	8	1876	90.1	38	6	3	7	80
93-20	140	150	18809	350	86	0.24	7	720	8	8	65	13	2326	266.3	42	10	6	12	76
93-20	150	160	18810	291	32	0.06	1	870	12	9	39	10	2405	347.9	52	10	6	12	87
93-20	160	170	18811	190	68	0.05	3	1520	11	7	44	6	1856	78.9	50	5	3	6	80
93-20	170	180	18812	364	29	0.11	1	720	4	9	53	11	2709	363.8	53	11	6	13	75
93-20	180	190	18813	424	108	0.05	3	560	38	120	57	9	1976	251.6	136	9	5	11	68
93-20	190	200	18814	280	110	0.06	5	540	8	8	50	7	1475	233.1	36	6	3	10	82
93-20	200	210	18815	354	131	0.03	1	380	9	4	29	4	525	61.0	26	3	2	3	51
93-20	210	220	18816	334	205	0.05	1	420	6	9	45	6	1372	161.7	35	6	4	8	71
93-20	220	230	18817	326	68	0.07	3	650	7	6	39	8	2172	160.5	44	7	4	9	81
93-20	230	240	18818	247	552	0.05	2	690	8	7	40	7	1267	110.8	37	6	4	6	74
93-20	240	250	18819	238	1128	0.03	3	490	8	5	34	6	562	69.9	31	5	4	5	69
93-20	250	260	18820	255	977	0.03	5	490	6	6	43	5	240	39.2	28	3	2	4	69
93-20	260	270	18821	204	106	0.04	6	570	5	6	33	4	356	44.9	33	3	2	5	79
93-20	270	280	18822	260	468	0.04	5	540	10	5	43	5	591	50.0	31	4	2	5	74
93-20	280	290	18823	242	45	0.07	1	620	5	3	30	4	1016	58.7	36	4	2	6	81
93-20	290	300	18824	304	455	0.07	1	600	6	4	33	5	900	57.9	39	4	3	5	75
93-20	300	310	18825	368	245	0.02	3	520	8	4	47	5	211	27.9	15	3	1	6	114
93-20	310	320	18826	258	152	0.04	3	480	1	3	15	5	303	38.2	14	3	1	4	54
93-20	320	330	18827	262	244	0.08	3	600	7	6	24	7	1009	54.0	25	5	3	6	92
93-20	330	340	18828	292	167	0.11	2	630	9	7	31	8	1058	59.5	29	6	2	7	94
93-20	340	350	18829	262	116	0.06	3	480	8	4	20	6	447	45.2	21	4	2	6	101
93-20	350	360	18830	256	422	0.05	5	330	12	4	36	7	102	27.1	13	3	1	6	107
93-20	360	370	18831	150	177	0.05	4	190	5	4	21	5	38	12.0	2	2	1	4	73
93-20	370	380	18832	248	225	0.05	5	390	7	6	20	8	310	47.3	24	4	1	6	107
93-20	380	390	18833	237	196	0.06	7	350	10	5	18	6	445	46.8	24	5	1	7	106
93-20	390	400	18834	306	66	0.04	6	690	6	10	22	8	1169	138.6	40	7	3	9	73
93-20	400	410	18835	256	365	0.05	11	830	12	9	31	9	512	66.0	23	6	2	6	86
93-20	410	420	18836	360	67	0.06	8	900	8	6	62	11	332	79.2	26	7	2	8	104
93-20	420	430	18837	354	290	0.09	7	800	13	7	158	10	253	50.0	24	6	2	6	76

II-257

MIN-EN LABORATORIES
705 W. 15th St.
North Vancouver, B.C.
Phone: 980-5814

Huckleberry

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)		SAMPLE	Cu-ASSAY	AG	AL	AS	B	BA	BE	BI	CA	CD	CO	CU	FE	K	LI	MG
HOLE#	START	END	NAME	%	PPM	%	PPM	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	%	%	PPM	%
93-20	430	440	18838	0.101	1.2	1.00	9	6	345	0.3	1	2.07	0.1	4	861	0.95	0.17	8	0.68

352 - II

MIN-EN LABORATORIES

705 W. 15th St.

North Vancouver, B.C.

Phone: 980-5814

Huckleberry

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)		SAMPLE	MN	MO	NA	NI	P	PB	SB	SR	TH	TI	V	ZN	GA	SN	W	CR	
HOLE#	START	END	NAME	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM
93-20	430	440	18838	292	172	0.05	6	380	4	3	23	7	58	25.3	13	4	1	5	91	

652-II-259

MIN-EN LABORATORIES
 705 W. 15th St.
 North Vancouver, B.C.
 Phone: 980-5814

Huckleberry

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)		SAMPLE	Cu-ASSAY	AG	AL	AS	B	BA	BE	BI	CA	CD	CO	CU	FE	K	LI	MG
HOLE#	START	END	NAME	%	PPM	%	PPM	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	%	%	PPM	%
93-21	82	90	40501	0.754	1.4	1.31	1	5	148	0.2	1	1.45	0.1	20	6733	6.87	0.59	9	1.29
93-21	90	100	40502	0.705	2.6	1.65	1	5	208	0.1	1	2.09	0.1	22	6350	6.50	0.85	11	1.77
93-21	100	110	40503	0.885	4.2	0.97	1	4	82	0.2	1	2.11	0.1	10	7370	2.53	0.28	9	1.15
93-21	110	120	40504	0.348	1.0	1.71	1	5	129	0.2	3	2.35	0.1	18	3171	6.28	0.65	10	1.59
93-21	120	130	40505	0.427	2.2	1.49	1	4	248	0.1	1	1.75	0.1	16	4023	4.53	0.65	11	1.39
93-21	130	140	40506	0.340	2.6	1.45	1	7	407	0.2	2	2.47	0.1	13	3345	3.47	0.47	12	1.19
93-21	140	150	40507	0.318	2.1	1.43	1	5	190	0.2	4	1.54	0.1	15	2883	3.66	0.60	14	1.39
93-21	150	160	40508	0.294	1.9	1.20	1	4	140	0.2	3	1.44	0.1	12	2729	3.18	0.34	12	1.16
93-21	160	170	40509	0.336	2.1	0.93	1	4	142	0.2	1	1.76	0.1	13	3059	2.86	0.27	10	0.94
93-21	170	180	40510	0.358	1.9	0.88	1	3	81	0.2	1	1.79	0.1	9	3273	2.37	0.16	9	0.99
93-21	180	190	40511	0.405	2.3	0.97	1	3	64	0.2	1	1.61	0.1	10	3744	2.41	0.09	8	0.97
93-21	190	200	40512	0.382	2.1	0.89	1	3	130	0.1	1	1.42	0.1	9	3441	2.09	0.07	7	0.89
93-21	200	210	40513	0.360	1.9	1.47	1	4	109	0.3	1	2.23	0.1	7	3404	2.13	0.06	7	0.83
93-21	210	220	40514	0.176	1.6	1.80	1	5	235	0.5	2	4.12	0.1	6	1500	1.61	0.07	4	0.62
93-21	220	230	40515	0.467	2.8	2.91	1	8	268	0.6	1	2.76	0.1	9	4050	1.97	0.13	8	1.10
93-21	230	240	40516	0.341	1.8	1.18	1	4	173	0.3	1	1.44	0.1	12	3108	2.30	0.13	10	1.17
93-21	240	250	40517	0.461	3.0	1.20	1	4	91	0.4	1	1.76	0.1	12	4029	2.65	0.12	10	1.13
93-21	250	260	40518	0.409	2.2	1.14	1	4	96	0.2	1	1.40	0.1	13	3595	2.22	0.10	10	1.12

022-II

MIN-EN LABORATORIES
 705 W. 15th St.
 North Vancouver, B.C.
 Phone: 980-5811

Huckleberry

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)		SAMPLE	MN	MO	NA	NI	P	PB	SB	SR	TH	TI	V	ZN	GA	SN	W	CR
HOLE#	START	END	NAME	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM
93-21	82	90	40501	325	97	0.11	1	580	12	11	25	4	1777	377.7	41	9	6	15	101
93-21	90	100	40502	417	30	0.10	1	600	16	10	37	8	2466	376.8	44	11	7	14	81
93-21	100	110	40503	265	162	0.04	6	1080	14	12	38	6	859	99.6	34	4	2	8	92
93-21	110	120	40504	477	29	0.10	1	570	9	6	42	6	2216	337.7	37	10	6	13	68
93-21	120	130	40505	326	68	0.09	2	620	10	7	31	6	2131	180.6	35	8	5	9	75
93-21	130	140	40506	479	535	0.07	1	610	12	7	41	8	1372	93.0	43	7	4	7	74
93-21	140	150	40507	414	63	0.09	3	420	12	5	21	6	1849	113.6	41	6	4	9	78
93-21	150	160	40508	283	122	0.10	4	370	8	5	22	5	1342	82.1	37	5	3	8	116
93-21	160	170	40509	272	415	0.05	4	330	9	5	19	5	861	65.4	36	5	3	6	81
93-21	170	180	40510	296	100	0.06	8	920	12	6	27	6	602	72.9	32	4	3	8	128
93-21	180	190	40511	330	26	0.07	11	1070	9	7	52	6	862	81.6	32	5	2	8	105
93-21	190	200	40512	313	62	0.09	8	1060	10	6	146	6	1059	67.0	33	4	2	9	140
93-21	200	210	40513	330	81	0.07	10	1000	11	6	99	7	231	73.6	31	5	2	7	79
93-21	210	220	40514	573	73	0.07	7	800	15	6	60	5	44	48.6	25	5	2	5	52
93-21	220	230	40515	330	138	0.19	10	850	14	9	257	9	271	59.1	30	7	2	5	50
93-21	230	240	40516	332	209	0.08	9	950	13	6	155	7	748	63.1	33	5	3	6	82
93-21	240	250	40517	489	94	0.07	10	950	11	8	81	8	471	75.4	41	5	2	9	123
93-21	250	260	40518	321	100	0.09	10	960	12	6	94	6	833	65.8	38	5	2	6	69

102-11

MIN-EN LABORATORIES
 705 W. 15th St.
 North Vancouver, B.C.
 Phone: 980-5814

Huckleberry

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)		SAMPLE	Cu-ASSAY	AG	AL	AS	B	BA	BE	BI	CA	CD	CO	CU	FE	K	LI	MG
HOLE#	START	END	NAME	%	PPM	%	PPM	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	%	%	PPM	%
93-22	30	40	17501	0.225	1.7	1.57	1	5	179	0.3	1	3.47	0.1	8	2123	1.93	0.42	9	0.84
93-22	40	50	17502	0.228	1.4	2.00	1	6	261	0.3	1	1.69	0.1	12	2164	2.53	0.53	10	1.22
93-22	50	60	17503	0.423	2.4	1.34	1	5	215	0.3	1	1.51	0.1	12	3702	2.31	0.41	9	1.23
93-22	60	70	17504	0.227	1.6	2.31	1	6	495	0.3	1	1.89	0.1	18	2089	2.96	0.40	11	1.22
93-22	70	80	17505	0.220	1.7	1.79	1	6	412	0.3	1	1.26	0.1	12	2114	2.68	0.56	10	1.27
93-22	80	90	17506	0.149	1.1	1.54	1	5	610	0.3	4	1.03	0.1	11	1385	2.50	0.54	10	1.28
93-22	90	100	17507	0.279	1.6	1.45	1	5	338	0.3	1	1.15	0.1	16	2707	3.98	0.52	12	1.22
93-22	100	110	17508	0.242	1.2	0.99	1	4	165	0.3	1	1.13	0.1	9	2130	2.55	0.26	9	0.87
93-22	110	120	17509	0.320	1.5	0.81	1	3	89	0.3	1	1.53	0.1	9	2784	2.24	0.17	6	0.66
93-22	120	130	17510	0.293	1.3	0.78	1	3	53	0.2	1	1.08	0.1	10	2583	2.22	0.13	8	0.76
93-22	130	140	17511	0.241	1.1	0.69	1	2	67	0.2	1	1.22	0.1	7	1982	1.69	0.12	6	0.57
93-22	140	150	17512	0.150	0.7	0.76	1	2	129	0.2	1	1.09	0.1	6	1245	1.76	0.22	6	0.62
93-22	150	160	17513	0.255	1.3	0.89	1	2	142	0.3	1	0.95	0.1	10	2272	2.67	0.26	8	0.75
93-22	160	170	17514	0.236	1.0	0.92	1	3	180	0.2	1	0.92	0.1	10	2079	2.17	0.31	8	0.83
93-22	170	180	17515	0.424	2.0	1.43	1	5	340	0.3	1	1.00	0.1	15	3925	3.56	0.55	12	1.18
93-22	180	190	17516	0.113	0.5	1.24	1	4	362	0.3	2	0.92	0.1	10	948	3.33	0.40	10	0.93
93-22	190	200	17517	0.224	1.2	1.40	1	4	274	0.4	1	1.12	0.1	11	2015	2.70	0.47	11	1.14
93-22	200	210	17518	0.240	1.9	1.90	1	5	512	0.2	4	1.49	0.1	16	2235	3.45	0.67	11	1.34
93-22	210	220	17519	0.311	2.1	1.75	1	4	330	0.3	1	2.00	0.1	13	2744	2.78	0.44	9	1.12
93-22	220	230	17520	0.236	1.4	1.36	1	4	217	0.4	1	2.12	0.1	9	2027	2.03	0.30	8	0.84
93-22	230	240	17521	0.250	1.3	1.41	1	3	198	0.4	1	1.73	0.1	8	2292	1.88	0.18	9	1.00
93-22	240	250	17522	0.267	1.5	1.24	1	3	79	0.3	1	1.82	0.1	7	2369	1.54	0.12	8	0.86
93-22	250	260	17523	0.224	1.3	1.18	1	3	132	0.4	1	1.79	0.1	9	1865	1.83	0.20	7	0.84
93-22	260	270	17524	0.286	1.1	2.00	1	6	273	0.4	1	1.95	0.1	14	1911	3.50	0.54	9	1.43
93-22	270	280	17525	0.229	1.5	1.94	1	6	297	0.1	1	1.98	0.1	16	1927	4.37	0.68	9	1.54
93-22	280	290	17526	0.418	2.3	1.64	1	5	161	0.1	1	2.06	0.1	18	3311	4.55	0.32	7	1.25
93-22	290	300	17527	0.371	2.3	2.15	1	8	194	0.3	1	2.29	0.1	21	3173	5.92	0.46	8	1.53
93-22	300	310	17528	0.450	2.6	1.84	1	6	169	0.1	1	1.64	0.1	26	3868	6.01	0.57	9	1.53
93-22	310	320	17529	0.424	2.9	1.54	1	6	156	0.1	1	1.35	0.1	30	3781	6.53	0.53	8	1.34
93-22	320	330	17530	0.474	3.1	1.65	1	7	260	0.1	1	1.13	0.1	39	4357	7.35	0.46	8	1.39
93-22	330	340	17531	0.653	3.6	1.69	1	7	214	0.1	1	1.05	0.1	31	6139	6.70	0.62	9	1.45
93-22	340	350	17532	0.621	4.2	2.13	1	6	251	0.1	1	1.32	0.1	33	5551	5.44	0.57	10	1.67
93-22	350	360	17533	0.409	3.1	1.54	1	6	318	0.1	1	1.08	0.1	25	3705	4.60	0.61	8	1.30
93-22	360	370	17534	0.359	2.7	1.53	1	6	204	0.1	1	1.27	0.1	22	3182	4.95	0.58	9	1.50
93-22	370	380	17535	0.381	3.4	2.30	1	8	224	0.1	3	1.24	0.1	27	3446	5.91	0.59	12	2.31
93-22	380	390	17536	0.194	1.9	2.92	1	9	193	0.2	4	1.66	0.1	24	1710	3.92	0.50	11	2.05
93-22	390	400	17537	0.803	6.2	2.54	1	8	137	0.2	1	1.61	0.1	38	7860	5.05	0.37	11	1.64

22-11

MIN-EN LABORATORIES
 705 W. 15th St.
 North Vancouver, B.C. Huckleberry
 Phone: 980-5814

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)		SAMPLE	MN	MO	NA	NI	P	PB	SB	SR	TH	TI	V	ZN	GA	SN	W	CR
HOLE#	START	END	NAME	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM
93-22	30	40	17501	509	73	0.03	5	420	9	4	31	4	404	47.7	27	4	2	5	63
93-22	40	50	17502	349	46	0.06	1	510	3	2	28	6	691	68.5	30	5	2	5	65
93-22	50	60	17503	268	223	0.06	4	600	11	5	17	6	955	68.5	32	5	2	6	69
93-22	60	70	17504	323	24	0.14	1	770	12	4	35	7	1019	74.3	31	5	2	6	69
93-22	70	80	17505	291	36	0.11	2	430	8	3	22	5	1189	72.1	30	5	3	6	78
93-22	80	90	17506	273	45	0.09	2	410	10	2	17	4	1171	67.9	29	5	2	6	72
93-22	90	100	17507	368	33	0.04	4	900	6	4	14	5	773	74.6	34	5	3	7	87
93-22	100	110	17508	284	160	0.04	2	390	6	3	8	3	329	47.3	33	3	2	4	49
93-22	110	120	17509	265	46	0.04	1	850	6	4	12	3	249	44.7	31	2	2	5	86
93-22	120	130	17510	243	84	0.04	1	590	10	4	10	2	358	46.6	36	3	2	4	51
93-22	130	140	17511	249	73	0.04	1	410	9	3	9	2	143	32.9	30	2	1	4	77
93-22	140	150	17512	270	38	0.04	3	250	6	2	8	2	294	33.5	26	2	1	4	59
93-22	150	160	17513	300	51	0.05	2	290	5	3	8	2	773	48.4	35	4	2	5	81
93-22	160	170	17514	260	54	0.04	1	310	7	3	7	2	521	55.6	31	2	1	3	49
93-22	170	180	17515	348	29	0.04	2	340	3	5	10	5	893	101.9	32	5	3	5	51
93-22	180	190	17516	312	39	0.03	1	430	1	2	8	4	677	67.7	27	3	2	4	41
93-22	190	200	17517	295	79	0.06	2	450	7	3	12	4	892	75.7	28	5	2	5	55
93-22	200	210	17518	328	40	0.09	1	2130	5	4	29	6	1710	99.9	28	6	3	8	91
93-22	210	220	17519	355	44	0.06	1	600	8	4	23	4	836	68.0	30	5	3	4	45
93-22	220	230	17520	318	39	0.04	1	580	9	3	19	4	419	42.8	27	3	1	5	62
93-22	230	240	17521	264	84	0.05	1	740	10	4	25	3	169	36.4	30	3	1	3	37
93-22	240	250	17522	255	70	0.03	2	660	10	4	24	4	106	30.3	28	3	1	3	52
93-22	250	260	17523	300	52	0.04	1	510	8	3	36	4	142	41.8	28	3	1	3	43
93-22	260	270	17524	509	34	0.03	1	450	7	3	17	6	622	104.9	29	6	3	5	32
93-22	270	280	17525	388	66	0.08	1	540	5	4	26	8	1116	132.2	37	7	3	6	56
93-22	280	290	17526	548	22	0.04	1	750	12	6	31	8	701	120.0	43	7	3	5	45
93-22	290	300	17527	792	37	0.03	1	840	10	6	29	9	1262	195.0	47	9	4	8	71
93-22	300	310	17528	918	23	0.03	1	940	15	8	26	8	1477	152.1	53	8	4	8	70
93-22	310	320	17529	579	77	0.04	1	860	10	7	30	9	1809	145.1	47	9	5	8	69
93-22	320	330	17530	467	57	0.06	1	970	9	7	93	9	2145	175.6	50	9	5	9	69
93-22	330	340	17531	350	32	0.07	1	960	13	8	81	8	2229	207.5	50	10	5	9	58
93-22	340	350	17532	360	43	0.11	1	850	15	8	114	10	2358	182.1	44	9	4	9	65
93-22	350	360	17533	280	34	0.09	1	660	5	5	62	5	1987	117.2	37	7	4	8	75
93-22	360	370	17534	337	24	0.06	1	810	12	4	37	8	1917	120.1	40	7	4	6	61
93-22	370	380	17535	471	22	0.10	4	1330	7	5	103	11	3047	147.4	44	10	5	9	83
93-22	380	390	17536	311	44	0.28	18	870	7	3	87	11	1987	157.9	31	9	4	13	170
93-22	390	400	17537	322	101	0.25	10	870	14	11	69	10	2075	154.3	42	10	4	11	116

II - 263

MIN-EN LABORATORIES
 705 W. 15th St.
 North Vancouver, B.C.
 Phone: 980-5814

Huckleberry

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)		SAMPLE	Cu-ASSAY	AG	AL	AS	B	BA	BE	BI	CA	CD	CO	CU	FE	K	LI	MG
HOLE#	START	END	NAME	%	PPM	%	PPM	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	%	%	PPM	%
93-22	400	410	17538	0.225	1.7	1.52	1	6	69	0.1	4	1.51	0.1	26	2107	5.74	0.21	8	1.21
93-22	410	420	17539	0.397	2.3	1.89	1	6	180	0.1	1	1.26	0.1	25	3654	6.17	0.43	9	1.50

192-II

MIN-EN LABORATORIES

705 W. 15th St.

North Vancouver, B.C.

Phone: 980-5814

Huckleberry

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)		SAMPLE	MN	MO	NA	NI	P	PB	SB	SR	TH	TI	V	ZN	GA	SN	W	CR
HOLE#	START	END	NAME	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM
93-22	400	410	17538	453	18	0.09	1	600	4	3	50	7	2148	196.5	39	9	4	9	70
93-22	410	420	17539	370	33	0.11	1	670	6	5	59	8	2124	239.5	43	9	5	10	78

II-265-

MIN-EN LABORATORIES
 705 W. 15th St.
 North Vancouver, B.C. Huckleberry
 Phone: 980-5877

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)		SAMPLE	Cu-ASSAY	AG	AL	AS	B	BA	BE	BI	CA	CD	CO	CU	Fe	K	LI	MG
HOLE#	START	END	NAME	%	PPM	%	PPM	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	%	%	PPM	%
93-23	45	50	932301	0.054	1.1	1.18	1	5	325	0.3	7	1.20	0.1	22	466	2.65	0.40	7	0.76
93-23	50	55	932302	0.112	1.0	1.77	1	7	414	0.2	18	1.09	0.1	40	1000	5.34	0.68	13	1.25
93-23	55	60	932303	0.062	1.0	1.76	1	6	375	0.2	8	1.66	0.1	29	557	3.86	0.74	14	1.49
93-23	60	65	932304	0.042	1.2	2.31	1	8	344	0.2	10	2.24	0.1	23	415	3.90	0.70	15	1.29
93-23	65	70	932305	0.068	1.6	1.81	1	6	336	0.2	17	1.93	0.1	28	604	3.82	0.62	10	1.10
93-23	70	80	932306	0.091	1.4	1.46	1	6	410	0.3	7	1.89	0.1	24	798	3.05	0.45	11	0.97
93-23	80	90	932307	0.091	1.0	0.99	1	4	255	0.2	5	1.33	0.1	25	787	3.28	0.35	10	0.84
93-23	90	100	932308	0.053	0.8	1.22	1	5	205	0.2	7	1.33	0.1	26	458	3.92	0.47	12	1.04
93-23	100	110	932309	0.083	0.9	1.84	1	6	228	0.1	9	1.53	0.1	26	737	4.70	0.75	17	1.54

222-II

MIN-EN LABORATORIES
 705 W. 15th St.
 North Vancouver, B.C.
 Phone: 980-5814 Huckleberry

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)		SAMPLE	MN	MO	NA	NI	P	PB	SB	SR	TH	TI	V	ZN	GA	SN	W	CR
HOLE#	START	END	NAME	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM
93-23	45	50	932301	631	10	0.05	8	550	1	7	25	6	238	40.5	31	4	1	6	71
93-23	50	55	932302	581	7	0.08	4	420	1	9	31	8	869	128.7	30	7	1	10	97
93-23	55	60	932303	560	21	0.07	6	710	1	7	46	9	926	114.7	32	7	1	8	65
93-23	60	65	932304	340	3	0.18	6	1150	1	9	73	9	1040	95.8	23	8	1	7	71
93-23	65	70	932305	511	5	0.14	3	840	1	8	59	8	985	79.0	28	7	1	8	80
93-23	70	80	932306	339	6	0.11	3	730	1	7	65	8	645	60.3	23	5	1	7	72
93-23	80	90	932307	372	19	0.05	5	540	1	6	34	6	284	52.9	24	5	1	5	48
93-23	90	100	932308	430	43	0.07	1	650	1	7	38	7	648	73.2	26	6	1	6	55
93-23	100	110	932309	377	3	0.11	1	970	1	9	47	8	1052	115.3	24	8	2	8	79

492-II

MIN-EN LABORATORIES
 705 W. 15th St.
 North Vancouver, B.C.
 Phone: 980-5814 Huckleberry

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)		SAMPLE	Cu-ASSAY	AG	AL	AS	B	BA	BE	BI	CA	CD	CO	CU	FE	K	LI	MG
HOLE#	START	END	NAME	%	PPM	%	PPM	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	%	%	PPM	%
93-24	55	60	932401	0.028	0.6	2.07	1	8	193	0.2	8	1.87	0.1	27	247	4.62	0.43	11	1.45
93-24	60	65	932402	0.017	1.0	2.65	1	9	167	0.1	9	2.64	0.1	20	148	3.24	0.20	6	0.64
93-24	65	70	932403	0.019	0.6	1.69	1	7	251	0.3	8	1.43	0.1	23	171	4.04	0.32	10	1.08
93-24	70	75	932404	0.026	0.6	1.34	1	5	229	0.2	6	1.36	0.1	24	223	3.94	0.25	9	1.00
93-24	75	80	932405	0.054	0.6	1.79	1	7	203	0.1	8	1.60	0.1	34	457	4.94	0.44	13	1.37
93-24	80	90	932406	0.035	0.8	2.25	1	8	303	0.2	9	1.58	0.1	26	304	4.65	0.52	15	1.46
93-24	90	96	932407	0.028	0.9	3.02	1	10	282	0.3	11	1.89	0.1	19	259	4.70	0.57	13	1.50

II-268

MIN-EN LABORATORIES
 705 W. 15th St.
 North Vancouver, B.C.
 Phone: 980-5814 Huckleberry

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)		SAMPLE	MN	MO	NA	NI	P	PB	SB	SR	TH	TI	V	ZN	GA	SN	W	CR
HOLE#	START	END	NAME	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM
93-24	55	60	932401	411	4	0.11	5	720	1	9	57	10	556	106.4	20	7	1	8	62
93-24	60	65	932402	309	20	0.17	4	310	1	9	85	7	414	57.2	21	7	1	6	64
93-24	65	70	932403	456	12	0.12	2	270	1	7	39	7	642	80.1	26	6	1	8	86
93-24	70	75	932404	441	30	0.07	4	390	1	5	33	7	529	71.6	24	5	1	7	69
93-24	75	80	932405	391	5	0.09	3	270	1	8	43	8	801	126.6	19	7	1	9	92
93-24	80	90	932406	370	6	0.16	4	650	1	7	52	10	1041	101.5	20	8	1	8	67
93-24	90	96	932407	308	4	0.32	1	780	1	10	74	11	958	107.1	20	10	3	9	90

II-269

MIN-EN LABORATORIES
 705 W. 15th St.
 North Vancouver, B.C.
 Phone: 980-5814

Huckleberry

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)		SAMPLE	Cu-ASSAY	AG	AL	AS	B	BA	BE	BI	CA	CD	CO	CU	FE	K	LI	MG
HOLE#	START	END	NAME	%	PPM	%	PPM	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	%	%	PPM	%
93-26	110	115	17640	0.602	3.0	3.13	1	10	383	0.4	1	1.28	0.1	19	5753	5.22	0.83	17	1.95
93-26	115	120	17641	1.270	5.9	4.41	1	13	299	0.5	1	1.67	0.1	16	10000	4.92	0.86	20	2.91
93-26	120	125	17642	0.883	4.7	3.02	79	9	473	0.3	1	2.49	0.1	15	7949	3.83	0.89	16	1.98
93-26	125	130	17643	0.768	4.4	2.92	1	9	1569	0.1	1	2.27	0.1	17	6626	4.69	0.96	17	2.17
93-26	130	135	17644	1.004	5.8	4.05	1	12	571	0.4	1	1.93	0.1	21	8962	5.25	1.23	19	3.08

HOLE#	INTERVAL(feet)		SAMPLE	AU
HOLE#	START	END	NAME	ppb
93-26	110	115	17640	122
93-26	115	120	17641	265
93-26	120	125	17642	182
93-26	125	130	17643	140
93-26	130	135	17644	183

II-210

MIN-EN LABORATORIES
 705 W. 15th St.
 North Vancouver, B.C.
 Phone: 980-5814

Huckleberry

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)		SAMPLE	MN	MO	NA	NI	P	PB	SB	SR	TH	TI	V	ZN	GA	SN	W	CR
HOLE#	START	END	NAME	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM
93-26	110	115	17640	445	43	0.07	11	880	8	8	50	11	2159	204.4	44	10	8	13	157
93-26	115	120	17641	402	46	0.02	14	930	16	19	57	15	1808	244.1	40	11	8	12	70
93-26	120	125	17642	399	85	0.02	17	840	18	21	45	14	1316	177.2	68	9	4	10	70
93-26	125	130	17643	467	95	0.02	17	750	9	12	46	13	1653	183.8	45	9	4	9	72
93-26	130	135	17644	513	137	0.02	19	880	10	15	42	16	2658	207.2	50	10	5	12	82

172-II

MIN-EN LABORATORIES
 705 W. 15th St.
 North Vancouver, B.C. Huckleberry
 Phone: 980-5814

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)		SAMPLE	Cu-ASSAY	AG	AL	AS	B	BA	BE	BI	CA	CD	CO	CU	FE	K	LI	MG
HOLE#	START	END	NAME	%	PPM	%	PPM	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	%	%	PPM	%
93-27	20	25	932701	0.007	0.1	2.15	1	6	247	0.1	13	1.30	0.1	26	65	5.61	0.33	4	0.97
93-27	25	30	932702	0.014	0.1	3.08	1	8	453	0.1	12	1.59	0.1	24	127	6.24	0.48	4	1.28
93-27	30	35	932703	0.029	0.1	2.32	1	7	95	0.1	12	1.34	0.1	24	250	6.25	0.22	6	1.30
93-27	35	40	932704	0.026	0.1	2.63	1	9	131	0.1	10	1.67	0.1	21	223	7.36	0.31	6	1.29
93-27	40	45	932705	0.010	0.1	2.63	1	9	213	0.1	10	1.41	0.1	19	84	6.75	0.35	5	1.23
93-27	45	50	932706	0.012	0.1	2.62	1	9	418	0.1	11	1.50	0.1	37	97	6.39	0.57	6	1.48
93-27	50	60	932707	0.008	0.3	2.66	1	9	316	0.2	7	2.38	0.1	29	47	5.24	0.37	6	1.27
93-27	60	70	932708	0.008	0.2	2.69	1	10	355	0.2	11	1.72	0.1	34	58	5.16	0.47	5	1.19

II - 272

MIN-EN LABORATORIES
 705 W. 15th St.
 North Vancouver, B.C. Huckleberry
 Phone: 980-5814

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)		SAMPLE	MN	MO	NA	NI	P	PB	SB	SR	TH	TI	V	ZN	GA	SN	W	CR
HOLE#	START	END	NAME	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM
93-27	20	25	932701	256	1	0.30	1	950	1	11	86	6	989	172.1	24	8	4	9	64
93-27	25	30	932702	295	2	0.40	1	850	3	12	103	10	1002	201.3	23	10	4	11	105
93-27	30	35	932703	370	1	0.26	1	800	1	11	64	9	1283	196.7	29	9	3	10	67
93-27	35	40	932704	609	1	0.31	1	840	1	9	71	8	1102	233.2	28	10	2	10	76
93-27	40	45	932705	335	1	0.38	1	990	1	10	70	8	1144	213.8	25	10	11	10	81
93-27	45	50	932706	309	1	0.24	1	820	3	9	81	8	1113	203.5	26	10	3	9	61
93-27	50	60	932707	368	1	0.20	1	850	2	9	93	9	665	157.7	25	9	2	7	44
93-27	60	70	932708	388	1	0.28	1	890	5	10	98	8	794	157.7	37	9	2	7	51

II-273

MIN-EN LABORATORIES
 705 W. 15th St.
 North Vancouver, B.C. Huckleberry
 Phone: 980-5614

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)		SAMPLE	Cu-ASSAY	AG	AL	AS	B	BA	BE	BI	CA	CD	CO	CU	FE	K	LI	MG
HOLE#	START	END	NAME	%	PPM	%	PPM	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	%	%	PPM	%
93-28	75	85	932801	0.021	0.1	2.78	1	9	489	0.2	11	0.99	0.1	31	194	7.36	0.79	8	2.02

142-II

MIN-EN LABORATORIES
 705 W. 15th St.
 North Vancouver, B.C.
 Phone: 980-5814

Huckleberry

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)		SAMPLE	MN	MO	NA	NI	P	PB	SB	SR	TH	TI	V	ZN	GA	SN	W	CR
HOLE#	START	END	NAME	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM
93-28	75	85	932801	362	1	0.20	2	670	1	10	51	11	1232	256.6	26	11	2	11	71

II-275-

MIN-EN LABORATORIES
 705 W. 15th St.
 North Vancouver, B.C.
 Phone: 980-5814

I.C.P. and Copper assay

New Canamin Resources

Huckleberry

HOLE#	INTERVAL(feet)		SAMPLE	Cu-ASSAY	AG	AL	AS	B	BA	BE	BI	CA	CD	CO	CU	FE	K	LI	MG
HOLE#	START	END	NAME	%	PPM	%	PPM	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	%	%	PPM	%
93-30	50	60	17601	0.239	1.4	1.58	1	7	378	0.1	1	0.93	0.1	17	2145	3.92	0.90	13	1.58
93-30	60	70	17602	0.443	2.7	1.40	1	7	269	0.1	1	1.61	0.1	18	4015	3.46	0.51	12	1.18
93-30	70	80	17603	0.757	4.4	1.47	1	8	425	0.1	1	1.66	0.1	21	6605	3.75	0.78	12	1.53
93-30	80	90	17604	0.792	5.0	2.10	1	9	481	0.1	1	1.87	0.1	21	7666	4.48	0.82	11	1.47
93-30	90	100	17605	0.658	3.2	2.23	1	10	446	0.1	1	1.95	0.1	27	6140	6.44	1.18	13	2.34
93-30	100	110	17606	0.829	3.0	1.77	1	8	295	0.1	1	1.47	0.1	28	7528	7.69	1.15	13	2.14
93-30	110	120	17607	0.995	3.5	1.75	1	9	144	0.1	1	1.70	0.1	27	8974	7.87	0.59	9	1.49
93-30	120	130	17608	0.802	4.4	2.32	1	9	440	0.1	1	2.77	0.1	28	7446	7.63	1.00	14	1.85
93-30	130	140	17609	1.022	4.8	2.44	1	10	577	0.1	1	2.06	0.1	32	8621	7.58	1.39	15	2.40
93-30	140	150	17610	1.030	3.9	1.75	1	8	214	0.1	1	1.67	0.1	28	9367	7.55	0.84	10	1.65
93-30	150	160	17611	0.554	2.4	2.41	1	11	284	0.1	1	2.84	0.1	25	4742	7.13	0.86	11	1.84
93-30	160	170	17612	0.562	2.6	1.71	1	8	201	0.1	1	2.31	0.1	22	4990	6.49	0.86	11	1.72
93-30	170	180	17613	0.430	0.8	1.12	1	6	154	0.1	1	1.27	0.1	23	3779	7.64	0.53	7	1.24
93-30	180	190	17614	0.601	1.6	1.32	1	7	158	0.1	1	1.37	0.1	23	5218	7.29	0.44	7	1.05
93-30	190	200	17615	0.379	0.7	1.56	1	7	164	0.1	1	1.62	0.1	20	3091	6.29	0.42	7	1.05
93-30	200	210	17616	0.623	2.4	1.70	1	7	209	0.1	1	1.87	0.1	22	5442	6.50	0.82	11	1.66
93-30	210	220	17617	0.626	4.0	1.13	1	8	170	0.1	1	2.42	0.1	15	5503	3.20	0.45	10	1.18
93-30	220	230	17618	0.387	1.1	1.83	1	8	241	0.1	3	1.64	0.1	25	3445	7.54	0.90	11	1.78
93-30	230	240	17619	0.875	3.3	1.87	1	8	361	0.1	1	1.62	0.1	30	7930	8.45	1.12	12	2.05
93-30	240	250	17620	0.748	3.6	2.13	1	9	358	0.1	1	2.27	0.1	25	6476	6.58	0.70	13	1.42
93-30	250	260	17621	0.221	1.7	1.15	1	7	178	0.1	3	1.58	0.1	12	1910	2.75	0.35	10	0.97
93-30	260	270	17622	0.631	3.6	1.07	1	7	149	0.1	1	1.55	0.1	15	5336	3.39	0.30	9	0.96
93-30	270	280	17623	0.459	3.0	1.93	1	8	405	0.1	1	1.43	0.1	21	4183	5.37	0.95	13	1.72
93-30	280	290	17624	0.752	3.4	2.52	1	10	394	0.1	1	1.60	0.1	33	6699	9.72	1.37	17	2.15
93-30	290	300	17625	0.738	3.4	1.69	1	7	339	0.1	1	2.02	0.1	26	6492	7.03	0.90	14	1.91
93-30	300	310	17626	0.788	3.2	2.21	1	8	390	0.1	1	2.08	0.1	30	6639	8.63	1.42	18	2.53
93-30	310	320	17627	0.517	1.9	2.33	1	8	185	0.1	1	1.80	0.1	22	4634	7.00	0.75	12	1.68
93-30	320	330	17628	0.334	2.5	3.71	1	11	390	0.1	4	2.23	0.1	22	3328	5.97	0.87	15	1.67
93-30	330	340	17629	0.596	3.2	2.52	1	8	361	0.1	1	2.04	0.1	26	5567	7.46	1.17	15	2.37
93-30	340	350	17630	0.702	3.9	1.35	1	6	236	0.1	1	1.64	0.1	19	6292	4.14	0.62	12	1.56

11-276

MIN-EN LABORATORIES
 705 W. 15th St.
 North Vancouver, B.C. Huckleberry
 Phone: 980-5814

I.C.P. and Copper assay

New Canamin Resources

HOLE#	INTERVAL(feet)		SAMPLE	MN	MO	NA	NI	P	PB	SB	SR	TH	TI	V	ZN	GA	SN	W	CR
HOLE#	START	END	NAME	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM
93-30	50	60	17601	371	62	0.06	1	230	7	2	21	7	1606	115.6	37	6	3	8	72
93-30	60	70	17602	274	39	0.08	2	350	12	6	31	7	1561	101.2	36	6	3	8	78
93-30	70	80	17603	270	317	0.07	4	700	11	9	37	8	2172	107.6	35	8	4	9	80
93-30	80	90	17604	249	210	0.19	2	900	15	10	66	8	2755	122.6	42	9	5	11	90
93-30	90	100	17605	382	161	0.15	2	750	7	8	71	10	3810	367.3	53	12	7	15	103
93-30	100	110	17606	407	65	0.11	1	620	11	11	51	10	3532	422.3	56	13	7	17	113
93-30	110	120	17607	470	27	0.13	1	670	18	13	56	7	2732	422.5	63	11	6	16	88
93-30	120	130	17608	434	108	0.10	1	510	13	12	81	10	3432	357.1	53	14	7	15	110
93-30	130	140	17609	369	109	0.12	5	630	18	12	65	12	4133	411.1	60	14	7	17	107
93-30	140	150	17610	342	54	0.16	1	680	9	14	77	9	3121	422.0	59	11	6	16	107
93-30	150	160	17611	428	207	0.15	1	570	12	8	218	11	3034	388.9	38	13	6	15	82
93-30	160	170	17612	371	97	0.15	1	570	4	8	57	8	2601	321.5	42	11	6	15	119
93-30	170	180	17613	381	49	0.10	1	580	5	5	44	5	2435	412.4	45	10	5	13	79
93-30	180	190	17614	366	87	0.16	1	570	15	8	54	5	2314	392.3	44	9	5	16	96
93-30	190	200	17615	318	64	0.19	1	550	4	4	93	7	2100	369.2	39	9	4	12	82
93-30	200	210	17616	332	113	0.12	1	700	11	8	63	9	2316	349.2	41	10	5	13	96
93-30	210	220	17617	218	615	0.05	5	1360	13	8	57	7	1921	109.8	35	7	4	8	57
93-30	220	230	17618	358	153	0.14	1	570	8	6	58	9	2911	449.6	47	12	7	15	107
93-30	230	240	17619	387	25	0.08	1	610	10	11	57	10	3698	447.4	57	13	7	16	96
93-30	240	250	17620	371	73	0.11	1	630	12	10	80	10	2778	310.1	46	10	5	14	96
93-30	250	260	17621	286	183	0.07	1	460	10	4	44	5	1502	72.2	32	5	4	8	104
93-30	260	270	17622	242	216	0.07	1	650	10	7	34	4	1991	88.2	39	6	4	8	65
93-30	270	280	17623	321	140	0.14	3	520	10	6	37	9	3048	227.3	40	10	5	13	101
93-30	280	290	17624	542	99	0.15	1	600	9	9	58	10	4192	448.5	51	15	10	18	104
93-30	290	300	17625	352	176	0.05	1	590	6	9	44	11	2940	347.4	51	11	7	14	100
93-30	300	310	17626	460	182	0.06	1	670	8	9	54	13	4165	446.8	51	15	9	16	86
93-30	310	320	17627	391	269	0.21	1	590	5	7	52	12	2609	337.0	42	12	8	13	87
93-30	320	330	17628	405	109	0.34	1	590	2	6	81	14	3094	230.0	39	13	7	11	87
93-30	330	340	17629	414	73	0.16	2	570	9	8	78	13	3498	357.9	39	13	8	15	128
93-30	340	350	17630	286	248	0.06	5	1010	6	8	39	7	2643	161.8	36	8	11	10	95

U-277

MIN-EN LABORATORIES
 705 W. 15th St.
 North Vancouver, B.C.
 Phone: 980-5814

MIN-EN LABORATORIES
 705 W. 15th St.
 North Vancouver, B.C.
 Phone: 980-5814

I.C.P. and Copper assay

New Canamin Resources

Huckleberry

HOLE#	INTERVAL(feet)		SAMPLE	Cu-ASSAY	AG	AL	AS	B	BA	BE	BI	CA	CD	CO	CU	FE	K	LI	MG
HOLE#	START	END	NAME	%	PPM	%	PPM	PPM	PPM	PPM	PPM	%	PPM	PPM	PPM	%	%	PPM	%
92-21V	220	230	40401	0.253	1.6	0.71	3	3	71	0.3	3	1.50	0.1	10	2027	2.37	0.06	8	0.96
92-21V	230	240	40402	0.182	1.5	0.77	1	5	56	0.3	8	1.49	0.1	12	1560	2.49	0.06	8	0.92
92-21V	240	250	40403	0.194	1.7	0.85	1	5	51	0.4	6	1.76	0.1	12	1745	2.53	0.08	9	0.99
92-21V	250	260	40404	0.377	2.9	0.93	1	6	68	0.4	1	1.88	0.1	12	3694	2.91	0.09	10	1.03
92-21V	260	270	40405	0.251	2.0	0.88	4	6	62	0.3	7	1.77	0.1	13	2427	2.66	0.08	10	1.02
92-21V	270	280	40406	0.214	1.7	0.96	1	6	68	0.4	11	1.83	0.1	14	1868	2.80	0.07	9	1.08
92-21V	280	290	40407	0.315	2.1	0.90	1	4	57	0.4	3	1.97	0.1	14	2866	2.86	0.08	10	1.12
92-21V	290	300	40408	0.236	1.3	0.87	1	6	46	0.3	4	1.94	0.1	14	2199	2.99	0.07	10	1.06

312-II

MIN-EN LABORATORIES
 705 W. 15th St.
 North Vancouver, B.C.
 Phone: 980-5814


Huckleberry

I.C.P. and Copper assay



New Canamin Resources

HOLE#	INTERVAL(feet)		SAMPLE	MN	MO	NA	NI	P	PB	SB	SR	TH	TI	V	ZN	GA	SN	W	CR
HOLE#	START	END	NAME	PPM	PPM	%	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM	PPM
92-21V	220	230	40401	333	54	0.07	11	960	13	7	57	9	718	61.9	36	4	3	5	62
92-21V	230	240	40402	272	45	0.11	10	1020	17	9	65	10	1045	69.3	34	5	3	7	79
92-21V	240	250	40403	337	261	0.12	9	1050	17	10	45	10	1139	71.8	34	6	4	8	100
92-21V	250	260	40404	505	67	0.11	9	1070	21	12	63	9	924	78.2	44	6	4	8	105
92-21V	260	270	40405	348	58	0.13	8	1070	26	11	73	12	1180	86.4	44	6	4	10	139
92-21V	270	280	40406	467	45	0.13	9	1010	19	11	84	12	1440	132.4	39	7	5	12	121
92-21V	280	290	40407	418	34	0.09	10	1080	17	9	65	11	1243	149.4	40	7	3	11	96
92-21V	290	300	40408	467	55	0.09	7	1080	17	8	54	12	1023	161.7	39	6	5	9	85

II - 279

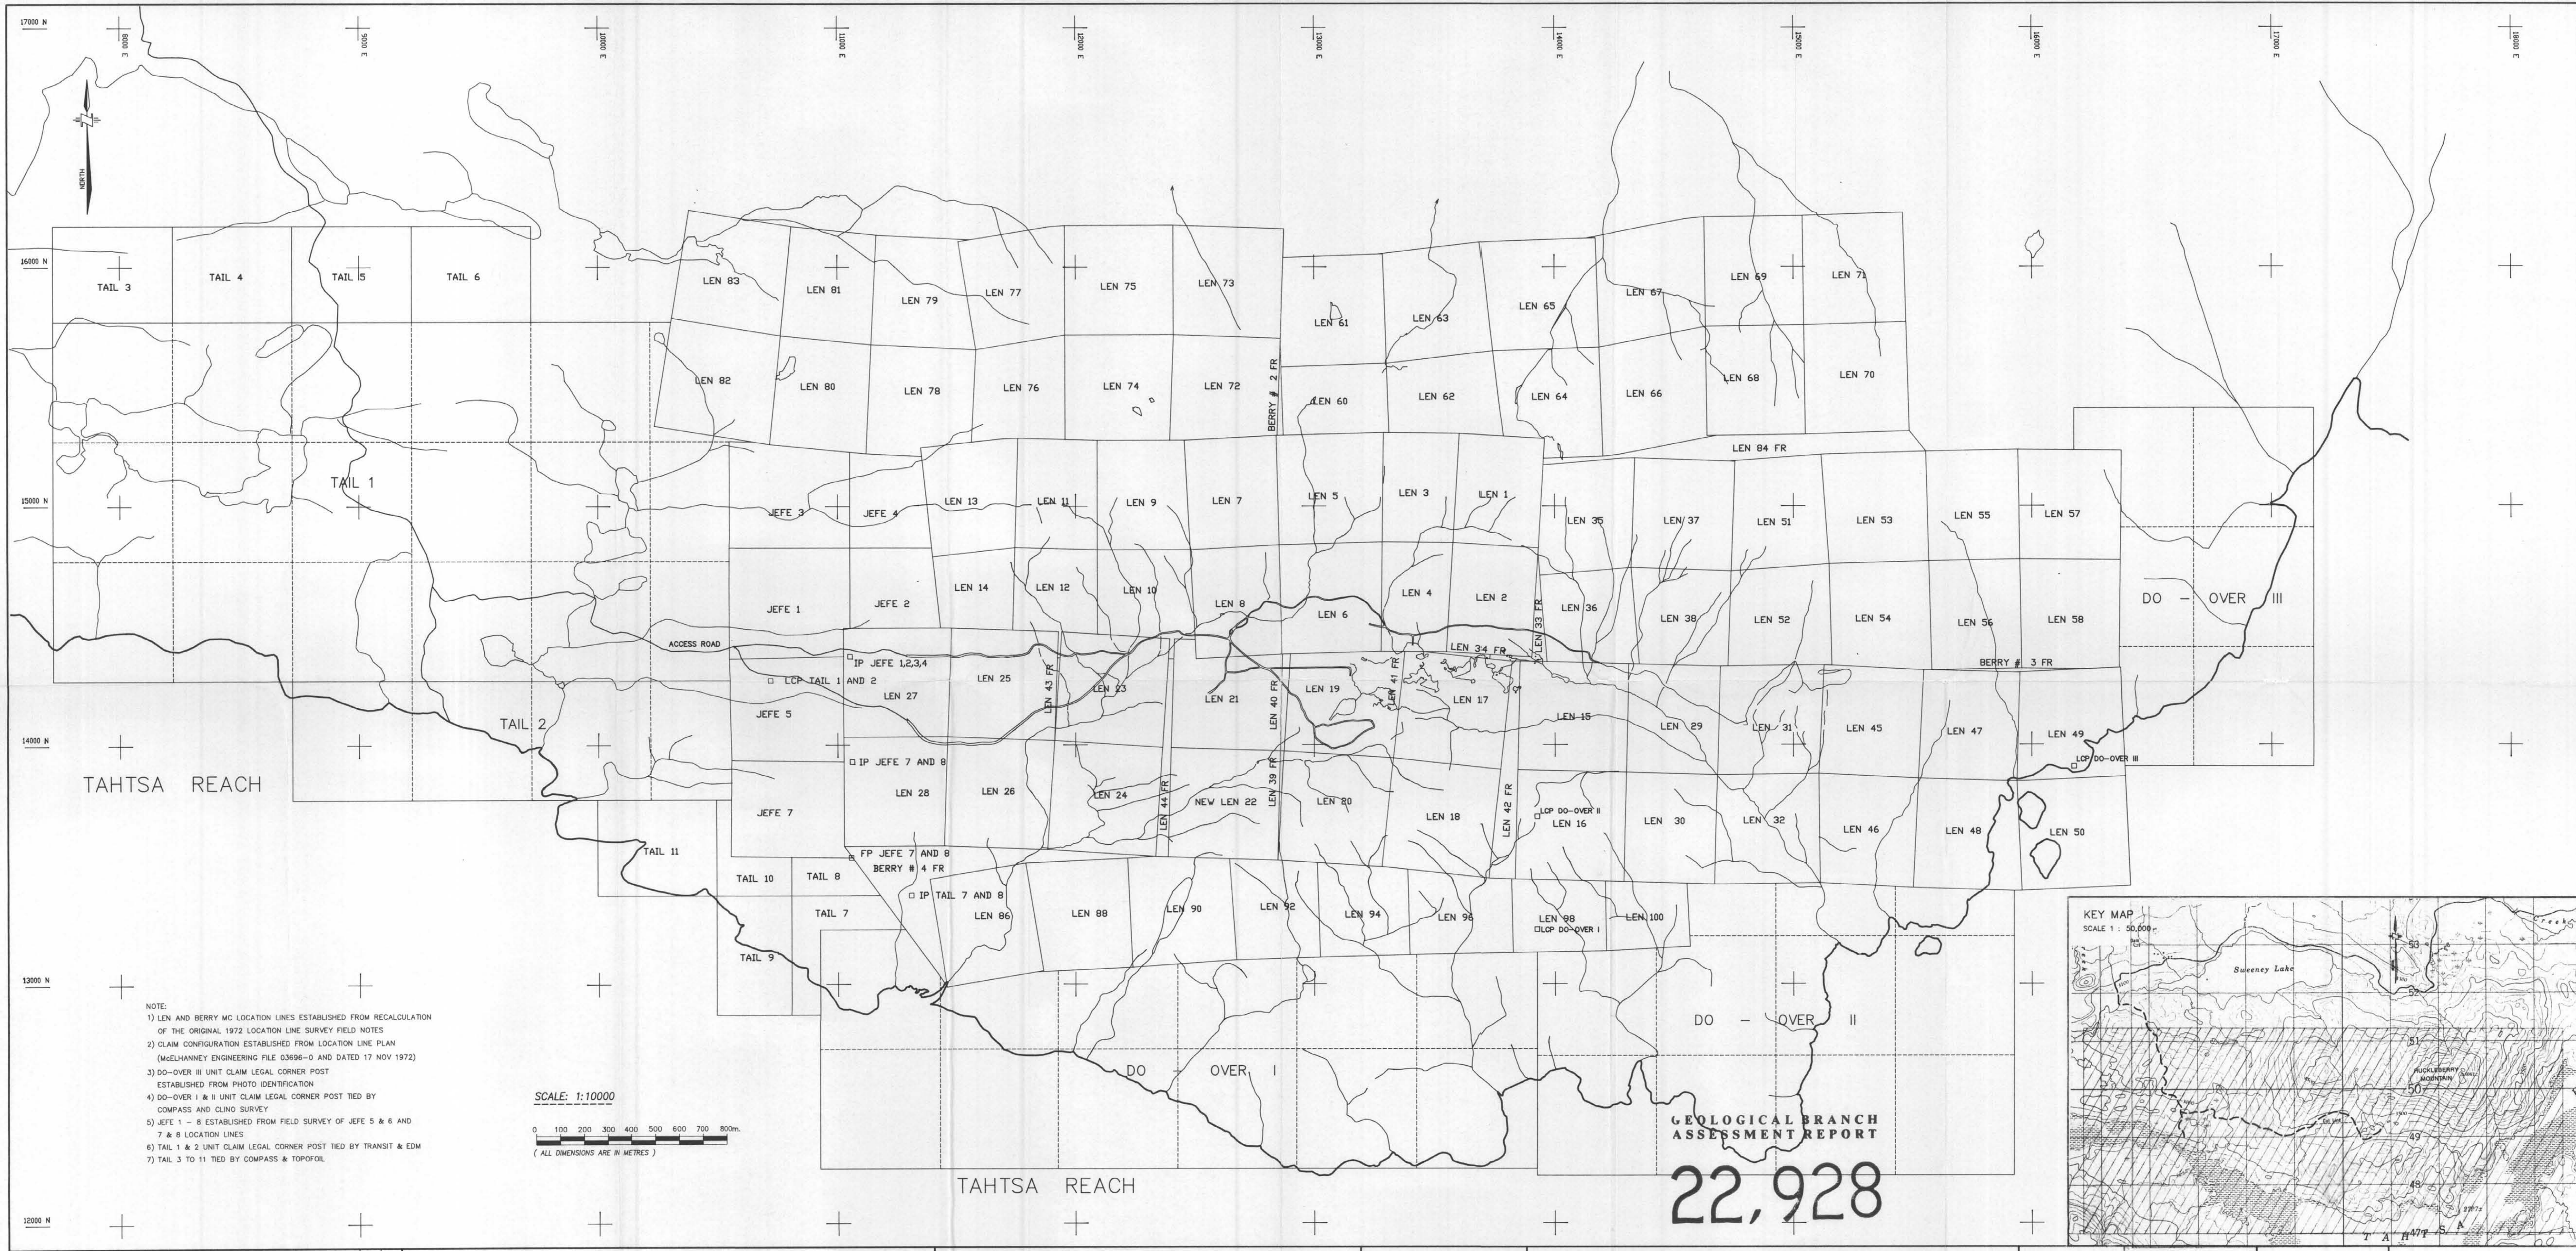

- NOTE:
- 1) LEN AND BERRY MC LOCATION LINES ESTABLISHED FROM RECALCULATION OF THE ORIGINAL 1972 LOCATION LINE SURVEY FIELD NOTES
 - 2) CLAIM CONFIGURATION ESTABLISHED FROM LOCATION LINE PLAN (McELHANNEY ENGINEERING FILE 03696-0 AND DATED 17 NOV 1972)
 - 3) DO-OVER III UNIT CLAIM LEGAL CORNER POST ESTABLISHED FROM PHOTO IDENTIFICATION
 - 4) DO-OVER I & II UNIT CLAIM LEGAL CORNER POST TIED BY COMPASS AND CLINO SURVEY
 - 5) JEFE 1 - 8 ESTABLISHED FROM FIELD SURVEY OF JEFE 5 & 6 AND 7 & 8 LOCATION LINES
 - 6) TAIL 1 & 2 UNIT CLAIM LEGAL CORNER POST TIED BY TRANSIT & EDM
 - 7) TAIL 3 TO 11 TIED BY COMPASS & TOPOFOIL

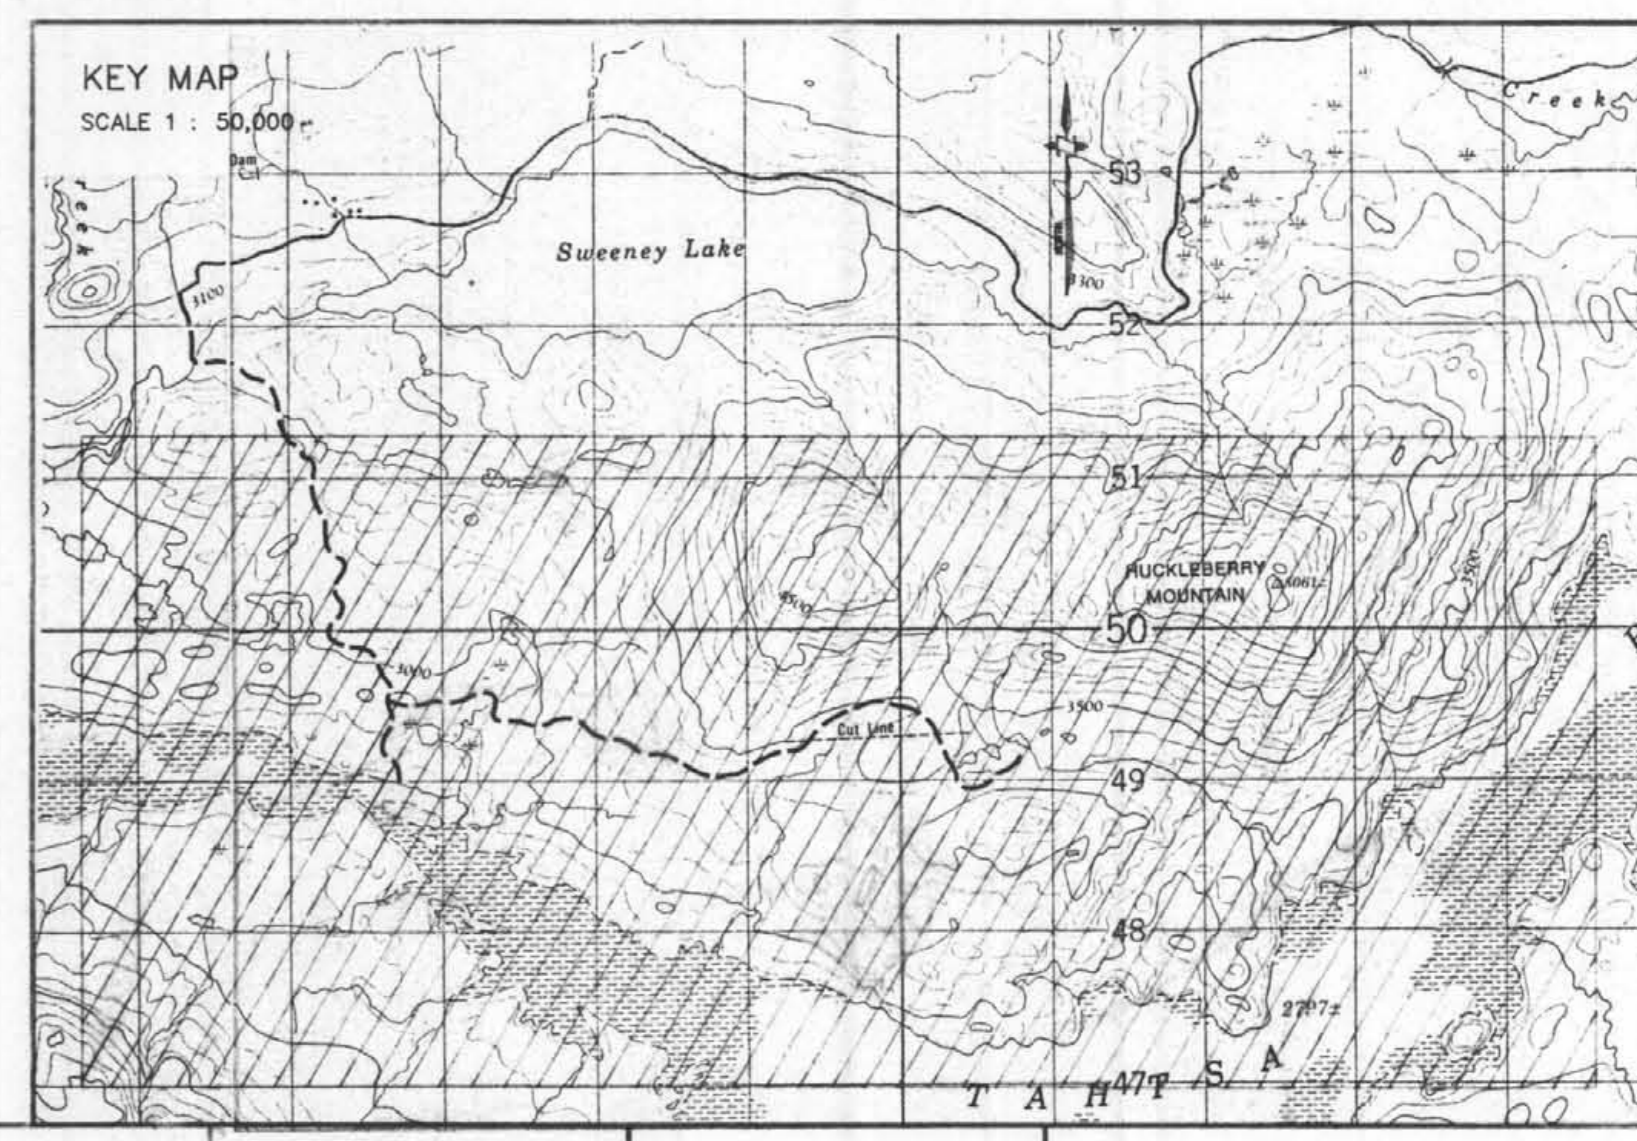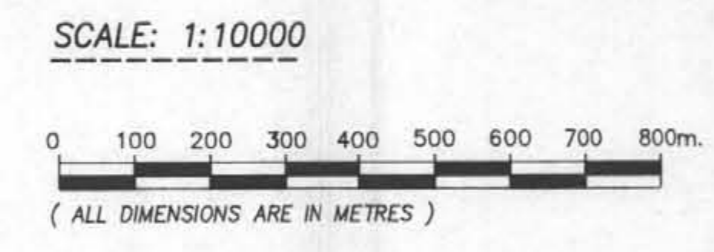

GEOLOGICAL BRANCH ASSESSMENT REPORT

22,928


No.	Date	Revision	Dr.	Ch.
1	May19/93	Addition of TAIL 1 to 11 Mineral Claims	WLK	JDC

McELHANNEY ENGINEERING SERVICES LTD.
 13160-88th AVENUE, SURREY, B.C. V3W 3K3 TEL: (604) 596-0391 FAX: (604) 596-8853



NEW CANAMIN RESOURCES LTD.
 LOCATION LINE COMPOSITE
 HUCKLEBERRY MOUNTAIN

MESL DWC No.	260-007	Designed	WLK	Job No.	410-00260
Drawn	WLK	Scale	1:10000	Date	7 JUN 1993
Checked	JDC	Revision	1		
Approved	RRS				

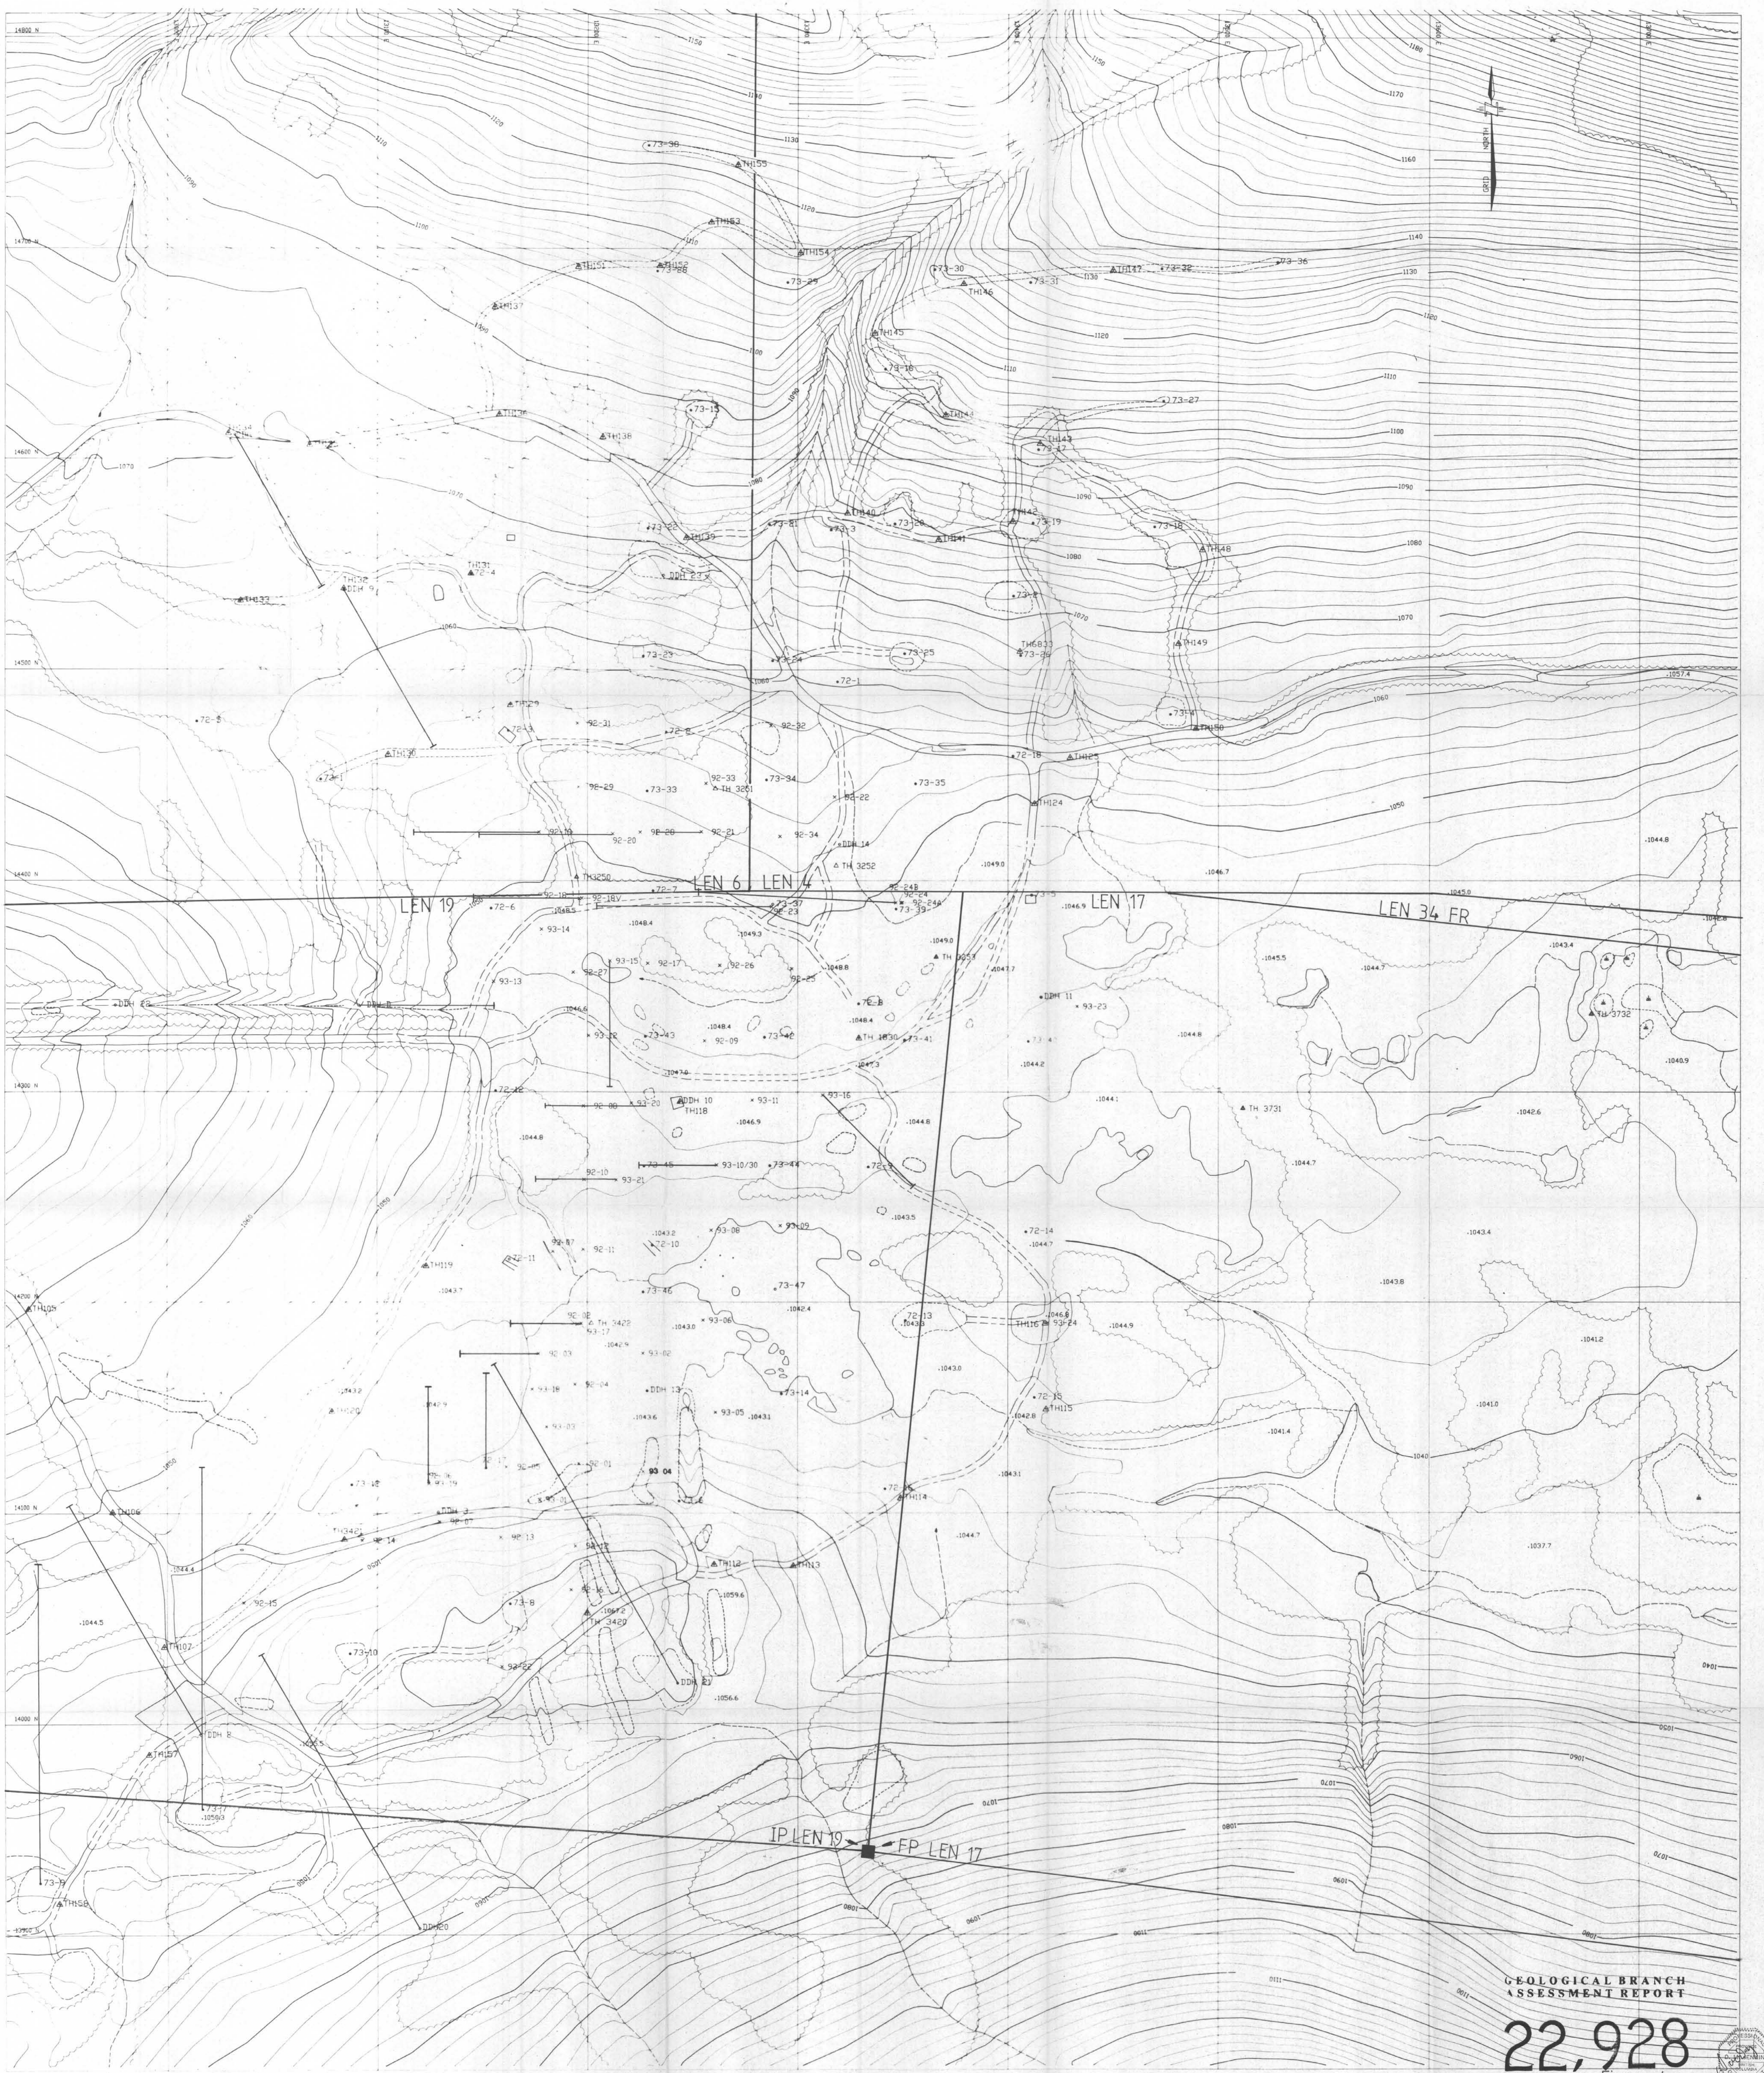

GEOLOGICAL BRANCH
ASSESSMENT REPORT

22,928
Figure 4



NEW CANAMIN RESOURCES LTD.

HUCKLEBERRY MTN.

DRILL HOLE LOCATIONS

- ▲ TRAVERSE POINT
- DRILL HOLE SURVEY 1992
- DRILL HOLE FROM EXISTING PLANS
- REF. # 1 5/11/28/92
- REF. # 2 2/28/92
- REF. # 3 1/28/92
- REF. # 4 1/28/92
- REF. # 5 1/28/92
- REF. # 6 1/28/92
- REF. # 7 1/28/92
- REF. # 8 1/28/92
- REF. # 9 1/28/92
- REF. # 10 1/28/92
- REF. # 11 1/28/92
- REF. # 12 1/28/92
- REF. # 13 1/28/92
- REF. # 14 1/28/92
- REF. # 15 1/28/92
- REF. # 16 1/28/92
- REF. # 17 1/28/92
- REF. # 18 1/28/92
- REF. # 19 1/28/92
- REF. # 20 1/28/92
- REF. # 21 1/28/92
- REF. # 22 1/28/92
- REF. # 23 1/28/92
- REF. # 24 1/28/92
- REF. # 25 1/28/92
- REF. # 26 1/28/92
- REF. # 27 1/28/92
- REF. # 28 1/28/92
- REF. # 29 1/28/92
- REF. # 30 1/28/92
- REF. # 31 1/28/92
- REF. # 32 1/28/92
- REF. # 33 1/28/92
- REF. # 34 1/28/92
- REF. # 35 1/28/92
- REF. # 36 1/28/92
- REF. # 37 1/28/92
- REF. # 38 1/28/92
- REF. # 39 1/28/92
- REF. # 40 1/28/92
- REF. # 41 1/28/92
- REF. # 42 1/28/92
- REF. # 43 1/28/92
- REF. # 44 1/28/92
- REF. # 45 1/28/92
- REF. # 46 1/28/92
- REF. # 47 1/28/92
- REF. # 48 1/28/92
- REF. # 49 1/28/92
- REF. # 50 1/28/92


CLAIM LINES SCALED FROM PLOT OF LEGAL SURVEY

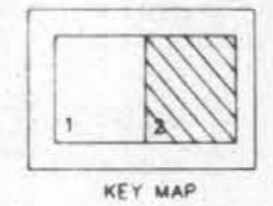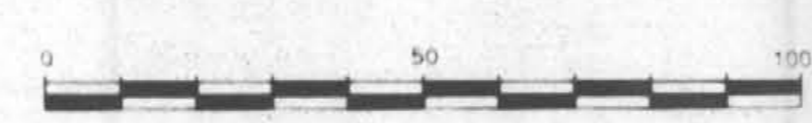

McElhanney Engineering Services Ltd.
13160-88th Avenue, Surrey, B.C. V3W 3K3 TEL: (604)596-0391
Compiled from 1 : 15,000 scale photography taken in 1973

MAP SCALE 1 : 1000
DATE COMPLETED JULY 1992

CONTOUR INTERVAL 2 metre
SHEET NUMBER 2 of 2

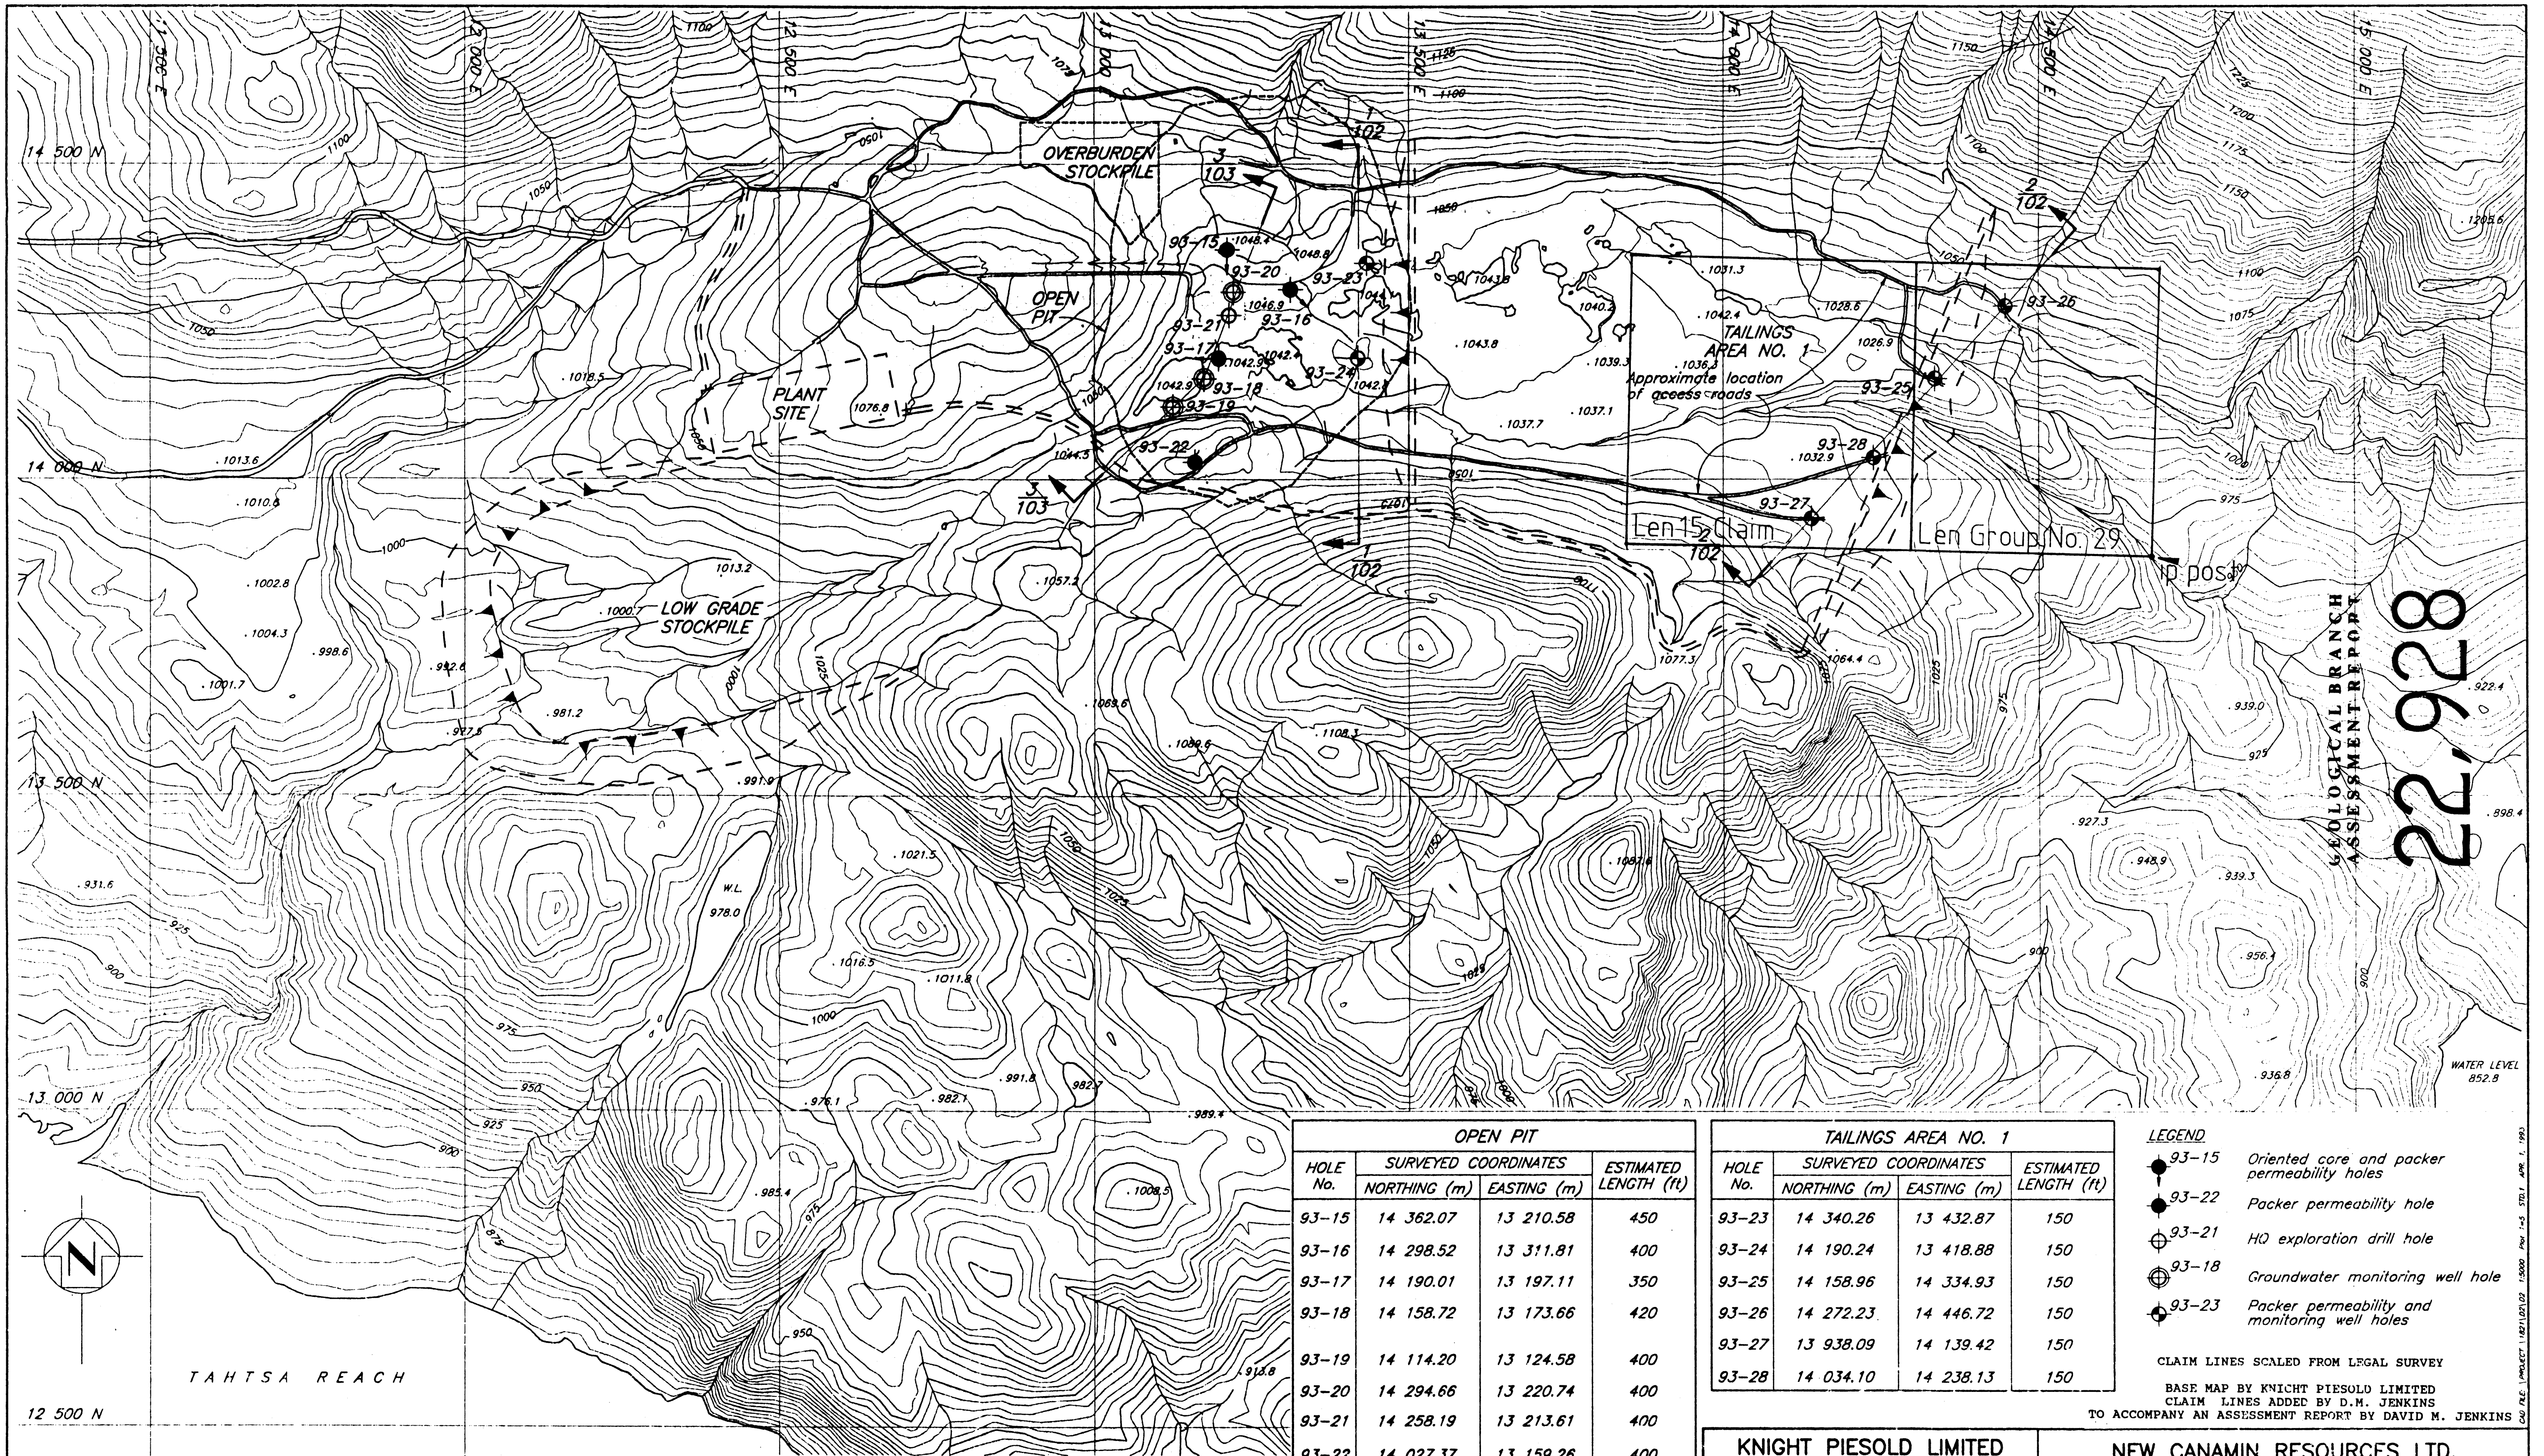

GEOLOGICAL BRANCH ASSESSMENT REPORT


22,928

OPEN PIT			
HOLE No.	SURVEYED COORDINATES		ESTIMATED LENGTH (ft)
	NORTHING (m)	EASTING (m)	
93-15	14 362.07	13 210.58	450
93-16	14 298.52	13 311.81	400
93-17	14 190.01	13 197.11	350
93-18	14 158.72	13 173.66	420
93-19	14 114.20	13 124.58	400
93-20	14 294.66	13 220.74	400
93-21	14 258.19	13 213.61	400
93-22	14 027.37	13 159.28	400

TAILINGS AREA NO. 1			
HOLE No.	SURVEYED COORDINATES		ESTIMATED LENGTH (ft)
	NORTHING (m)	EASTING (m)	
93-23	14 340.26	13 432.87	150
93-24	14 190.24	13 418.88	150
93-25	14 158.96	14 334.93	150
93-26	14 272.23	14 446.72	150
93-27	13 938.09	14 139.42	150
93-28	14 034.10	14 238.13	150

- LEGEND**
- 93-15 Oriented core and packer permeability holes
 - 93-22 Packer permeability hole
 - ⊕ 93-21 HQ exploration drill hole
 - ⊕ 93-18 Groundwater monitoring well hole
 - ⊕ 93-23 Packer permeability and monitoring well holes

CLAIM LINES SCALED FROM LEGAL SURVEY
 BASE MAP BY KNIGHT PIESOLD LIMITED
 CLAIM LINES ADDED BY D.M. JENKINS
 TO ACCOMPANY AN ASSESSMENT REPORT BY DAVID M. JENKINS

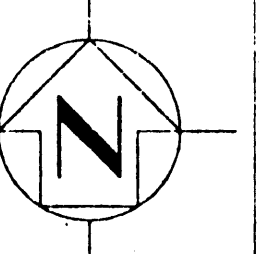

KNIGHT PIESOLD LIMITED
 CONSULTING ENGINEERS - VANCOUVER, B.C.

NEW CANAMIN RESOURCES LTD.

DESIGNED KJB/MDG
 DRAWN RDT/NAR
 CHECKED
 APPROVED

HUCKLEBERRY PROJECT
 FIGURE 5
HYDROGEOLOGICAL / GEOTECHNICAL INVESTIGATIONS

DRG. NO.	DESCRIPTION	REV.	DATE	DESCRIPTION	APPROVED	REV.	DATE	DESCRIPTION	APPROVED
	REFERENCE DRAWINGS			REVISIONS				REVISIONS	

DATE **MAR. 11, 1993** SCALE AS SHOWN DRG. NO. **1821.101** REV. **D**