

24611

DIAMOND DRILLING REPORT (Interim)
FAIRVIEW PROJECT
(SILVER CROWN AND WINDER 2 MINERAL CLAIMS)
Osoyoos Mining Division, British Columbia
NTS 82E/4E


Latitude: 49° 12'N
Longitude 119° 38'W

on behalf of owner

OLIVER GOLD CORPORATION
Vancouver, B.C.
GEOLOGICAL SURVEY BRANCH
ASSESSMENT REPORT


24,611
by
F.R. Haggard, P. Eng.

February 1995

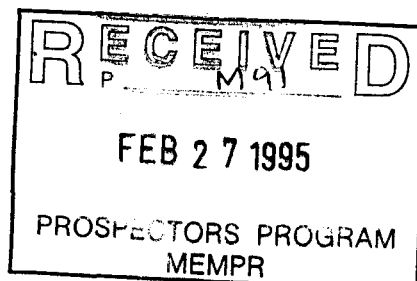

STATEMENT OF EXPLORATION EXPENDITURES

Meals, groceries	\$ 614
Accommodation	839
Vehicle operating and maintenance	2,064
Drilling	175,339
Consultant services	30,105
Assays and analyses	6,396
Communications/Office	831
Sample shipping	910
Field supplies	<u>517</u>
Total Exploration Expenditures	<u>\$217,615</u>

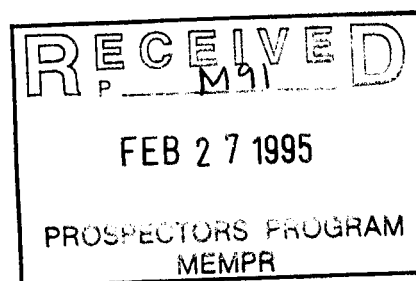

CONTENTS

	<u>Page No.</u>
INTRODUCTION	1
General	1
Location and Access	1
Property	1
History, Previous Exploration	1
GEOLOGY	2
Regional Geology	2
Property Geology	3
Quartz Veins and Mineralization	3
FALL 1994 EXPLORATION	4
REFERENCES	At End

TABLES

<u>TABLE</u>	<u>Page No.</u>
1 Drill Hole Summary - Silver Crown Area	At End
2 Drill Hole Intersections - Hangingwall Vein ...	At End
3 Drill Hole Intersections - Main Vein	At End

APPENDICES

APPENDIX

I Drill Logs	At End
II Assay Reports	At End
III Statement of Costs	Attach.

LIST OF FIGURES

<u>FIGURE</u>		<u>Page No.</u>
1	Property Location	At End
2	Fairview Crown Grants and Mineral Claims	At End
3	Regional Geology.....	At End
4	Property Geology.....	At End
5	Drill Hole Plan.....	At End
6	Section 8530N.....	At End
7	Section 8515N.....	At End
8	Section 8500N.....	At End
9	Section 8485N.....	At End
10	Section 8470N.....	At End
11	Section 8455N.....	At End
12	Section 8440N.....	At End
13	Section 8425N.....	At End
14	Section 8410N.....	At End
15	Section 8380N.....	At End
16	Section 8350N.....	At End

DIAMOND DRILLING REPORT (Interim)

FAIRVIEW PROJECT

Osoyoos Mining Division, British Columbia

INTRODUCTION

General

The Fairview Property, containing the historic Fairview-Stemwinder-Morningstar mining camp, is located in the southern Okanagan Valley, B.C. Exploration and mining in the area began in the late 1890's and continued intermittently until 1961; gold, silver and silica (smelter flux) have been produced. Exploration targets are high-grade auriferous shoots within an extensive quartz vein system to produce direct-shipping smelter feed.

This report briefly summarizes the property, it's geology and exploration history. Data from exploration during November and December, 1994 is presented and includes: drill logs, assay reports and surface plan and cross sections. Additional evaluation of the data is in progress.

Location and Access

The Fairview Property is located on the western side of the Okanagan Valley approximately 35 km south of Penticton and 6 km west of Oliver, B.C. (Fig. 1) The property is within map sheet area NTS 82E/4E in the Osoyoos Mining Division at latitude 49° 12'N and longitude 119° 38'W.

Access from Oliver is by the all-weather gravel Oliver-Cawston road and by various dirt roads on the property (Fig. 1).

Property

The Fairview property consists of 10 MSG recorded claims (45 units) and 29 Crown Grants, owned or under option by Oliver Gold Corporation, the present operator (Fig. 2). The MSG recorded claims and 24 Crown Grants are owned by Oliver Gold Corporation. Five Crown Grants on the Fairview property and seven surrounding the nearby Susie mine are under option from Asarco Exploration Co. of Canada Ltd.; terms include work commitments of \$50,000 and annual payments of \$10,000. Upon production, Asarco will receive a 3.5% N.S.R. (Asarco Fairview claims) or 4.5% N.S.R. (Susie mine claims).

History, Previous Exploration

Lode discoveries on the property date from the late 1880's and occur along a vein system which strikes over four kilometres. Three areas, Fairview, Stemwinder and Morningstar, have been mined at various times between 1895 and 1961; short exploration adits were also driven on the Brown Bear and Silver Crown claims. Production

totals 512,473 tonnes grading 3.99 g/tonne gold and 49.1 g/tonne silver (521,307 tons @ 0.12 oz/ton Au, 1.43 oz/ton Ag) (Tupper, 1991). Most of the production was from the Fairview mine and was utilized as flux at the Consolidated Mining and Smelting Company of Canada Ltd's (Cominco) smelter at Trail.

In 1986, associated predecessor companies of Oliver Gold Corporation acquired the Fairview and Morningstar properties from Cominco Ltd. and the Stemwinder property from Asarco Ltd. Initial exploration was directed at increasing the grade and tonnage of reserves within the Fairview mine and included diamond drilling and surface and underground mapping and sampling. Reserves within the Fairview mine are 1,694,055 tonnes @ 3.67 g/t Au and 38.4 g/t Ag (1,867,357 Tons @ 0.107 oz/T Au, 1.12 oz/T Ag), including a higher grade portion below 6 Level of 121,837 tonnes @ 5.01 g/t Au and 57.3 g/t Ag (134,302 Tons @ 0.146 oz/T Au, 1.67 oz/T Ag). The vein system north of Brown Bear adit was diamond drilled and the Brown Bear workings were extended (Mehner, 1986 to 1990 incl.).

In 1991, diamond drilling tested the vein system from the Fairview mine to the Morningstar mine. A potential high-grade ore shoot in the Hangingwall vein was indicated by widely spaced drill holes in the vicinity of the Brown Bear and Silver Crown adits. The Hangingwall vein in hole SC91-21 was 4.82 metres thick (true) and contained 49.78 g/tonne (1.452 oz/T) gold and 76.8 g/tonne (2.24 oz/T) silver; in hole SC91-17, it was 1.08 metres thick and contained 7.06 g/tonne (0.206 oz/T) gold and 116.6 g/tonne (3.40 oz/T) silver. Additional drilling was recommended (Tupper, 1991).

In early 1994, 13 diamond drill holes, totalling 1083.3 metres tested the prospective part of the Hangingwall (HWV) and nearby Main (MV) veins in the Brown Bear-Silver Crown area. Results indicated the presence of shoots on both veins near the Silver Crown adit; both shoots were open to grid south and at depth (Hassard, 1994). Holes intersecting the shoots are summarized, along with holes drilled in Nov. and Dec., 1994 in Tables 1-3.

GEOLOGY

Regional Geology

The Fairview area is underlain by Kobau Group metasediments which have been intruded by the Oliver pluton and the Fairview granodiorite plug (Fig. 3). The Kobau metasediments host the auriferous quartz veins and are also cut by various dykes and small granitic, dioritic and mafic stocks. The area has been regionally mapped by Bostock (1940) and Little (1961).

The Kobau Group extends southwards from the Oliver pluton to the International boundary, between the Okanagan River and the Similkameen River valley. The probably Carboniferous metasediments consist of a complex assemblage including: quartzites, schists, greenstones, marbles and phyllites. The structural history includes at least three discrete folding events and later brittle

faulting. Metamorphic grade does not exceed greenschist facies (Okulitch, 1969 and 1973; Mader et al, 1989).

The Jurassic Oliver pluton (155 Ma.) is a heterogeneous complex which includes several distinct lithologies; in the Fairview area the pluton is dominated by porphyritic granite and quartz monzonite phases. Regionally, it is considered to be part of the Nelson Plutonic event (Bostock, 1940). The slightly younger Fairview granodiorite (111±5 Ma.) is a small sub-circular plug about 4 kilometres in diameter. Jurassic ages for the plutons are after Armstrong (cited in Mader et al, 1989).

Property Geology

The Fairview property straddles a narrow, northwesterly trending, northeasterly dipping belt of Kobau Group metasediments 300 to 600 metres thick, which separates the Oliver pluton from the Fairview granodiorite (Fig. 4). Lithologies have been described in some detail by Tupper (1991), based on mapping by Okulitch (1969, 1973), Mehner (1986) and Mader et al (1989) and observations of various company mine geologists.

The Kobau Group metasediments host the Fairview gold- and silver-bearing quartz veins. On the property, stratigraphy strikes approximately 130°, is overturned and dips between 45° and 70° to the northeast. Three major units are recognized: upper mafic schist, lower quartzite and lower mafic schist (Mader et al. 1989).

The lower quartzite (KQ1) is the principal host of the auriferous quartz veins. It is a predominantly quartz-laminated unit with up to five percent micaceous partings and trace to two percent pyrite. Graphitic quartzite, limey tuffs and argillite also occur.

Cominco maps indicate shear zones sub-parallel stratigraphy in the Morning Star to Stemwinder areas. Drilling indicates graphitic and sericitic shear zones occur in the hangingwall of the quartz vein system near the Silver Crown adit (Hassard, 1994).

Quartz Veins and Mineralization

In general, three major quartz veins or vein zones occur along 4 kilometres of strike and are referred to as the Hangingwall Vein, Main Vein and Footwall Vein. These conform in general with the strike and dip of the schistosity of the host quartzites. Veins are discontinuous, locally sheared-out by subparallel faulting and also offset short distances along cross-faults. Veins commonly vary from a few centimetres up to three metres wide, however, in the Fairview mine, zones up to 15 metres (50 feet) wide are reported. Quartz veins, with negligible gold, exist in Fairview granodiorite (Wiley, 1982). Near the Silver Crown area of current interest, strikes are northwest and dips are approx. 60° northeast.

Gold is erratically distributed within, and occasionally adjacent to, the quartz veins where it is associated with pyrite.

The highest silver values tend to be associated with fine-grained galena + sphalerite and blebs of chalcopyrite. Coarse native gold occurs locally and contributes to a significant "nugget" effect.

Ore shoots have been recognized during mining and drilling of the Fairview, Stemwinder and Morning Star mines. Shearing and/or tectonic thickening are considered to be important in localizing shoots within the quartz vein system (Swanson, 1950; Irvine, 1960). Drilling in 1994 indicates shoots exist in the Hangingwall and Main veins near the Silver Crown workings; attitude, extent and grade are unknown. A shear might intersect the veins at a shallow angle near the thickest vein intersections below the Silver Crown workings (Hassard, 1994).

FALL 1994 EXPLORATION

Twenty-eight holes totalling 2,667.3 metres were drilled between Nov. 9 and Dec. 19, 1994 by Atlas Drilling of Kamloops, B.C. (Table 1). Holes were logged lithologically by the author and Mr. R.J. Beckett, P. Geol. All core was monitored for anomalous radioactivity; none was detected. Split core was fire-assayed by Bondar-Clegg of North Vancouver; samples with visible native gold were generally screened for metallics and fire-assayed. Assay intervals for the Hangingwall Vein (Table 2) and Main Vein (Table 3), are shown in logs and on cross sections; calculations use gold values screened for metallics where available. Lithologic logs and assay reports are attached as Appendices I and II respectively. A drill plan and cross sections (Figs. 5 to 16) are at the end.

Interpretation of the data is not complete. Longitudinal sections, in preparation, will be utilized to evaluate the potential of the Silver Crown area and to establish a possible mineral resource.

Clustering of high-grade intervals, several with visible gold, indicate the presence of shoots on the Hangingwall Vein between sections 8470N and 8410N (holes SC94-12, 13, 14, 16 and 36) and on the Main Vein between sections 8530N and 8470N (holes SC94-1, 2, 33, 37 and 38). Considerable structural disruption on veins is evident in holes to grid south and east. Many of the assays, and assay intervals, have low reliability as much core was lost in friable, shattered sheared zones. It is likely that any reasonable grade estimate will require test mining, due to recovery problems.

Respectfully submitted,



F.R. Hassard, P. Eng.

TABLE 1
DRILL HOLE SUMMARY
SILVER CROWN AREA

<u>Drill Hole</u>	<u>Location</u>	<u>Dip (°)</u>	<u>Length (m)</u>	<u>Date Collared</u>	<u>Date Completed</u>
<u>Previously Drilled Holes</u>					
SC91-17	8470N/ 93E	-47	70.6	16/02/91	17/02/91
SC91-18	8361N/ 101E	-44	76.1	17/02/91	17/02/91
SC94- 1	8500N/ 106E	-50	71.1	6/02/94	7/02/94
SC94- 2	8530N/ 111E	-50	68.9	7/02/94	8/02/94
SC94-11	8503N/ 123E	-65	89.9	18/02/94	19/02/94
SC94-12	8470N/ 131E	-60	100.6	19/02/94	20/02/94
SC94-13	8440N/ 121E	-68	102.4	20/02/94	22/02/94
<u>Fall 1994 Holes</u>					
SC94-14	8440N/ 97.0E	-60	75.3	9/11/94	10/11/94
SC94-15	8410N/ 92.5E	-45	78.0	10/11/94	11/11/94
SC94-16	8410N/131.0E	-63	110.0	11/11/94	13/11/94
SC94-17	8380N/124.5E	-56	101.2	13/11/94	14/11/94
SC94-18	8410N/160.0E	-60	142.0	15/11/94	16/11/94
SC94-19	8440N/154.0E	-63	131.4	17/11/94	18/11/94
SC94-20	8470N/152.0E	-64	135.3	19/11/94	21/11/94
SC94-21	8500N/161.0E	-57	128.9	21/11/94	22/11/94
SC94-22	8500N/161.0E	-72	154.2	22/11/94	24/11/94
SC94-23	8530N/136.5E	-53	92.4	25/11/94	26/11/94
SC94-24	8530N/156.0E	-62	120.7	26/11/94	28/11/94
SC94-25	8470N/162.0E	-70	160.3	28/11/94	30/11/94
SC94-26	8500N/ 62.0E	-67	30.5	30/11/94	1/12/94
SC94-27	8500N/115.0E	-59	77.4	1/12/94	2/12/94
SC94-28	8350N/133.0E	-60	111.3	3/12/94	4/12/94
SC94-29	8410N/113.5E	-56	91.4	4/12/94	5/12/94
SC94-30	8440N/ 66.0E	-53	45.7	5/12/94	6/12/94
SC94-31	8440N/114.5E	-62	87.0	6/12/94	7/12/94
SC94-32	8500N/ 80.0E	-57	38.4	7/12/94	7/12/94
SC94-33	8470N/112.0E	-54	78.0	8/12/94	9/12/94
SC94-34	8455N/130.0E	-63	106.7	9/12/94	10/12/94
SC94-35	8443N/134.0E	-63	115.8	10/12/94	11/12/94
SC94-36	8425N/126.5E	-63	102.4	12/12/94	13/12/94
SC94-37	8530N/ 79.5E	-46	28.7	13/12/94	13/12/94
SC94-38	8515N/108.5E	-50	64.0	13/12/94	15/12/94
SC94-39	8425N/109.5E	-60	85.3	15/12/94	16/12/94
SC94-40	8425N/144.0E	-60	113.7	17/12/94	19/12/94
SC94-41	8485N/ 98.0E	-60	61.3	19/12/94	20/12/94

Total Fall 1994 Drilling: 2,667.3m

TABLE 2

DRILL HOLE INTERSECTIONS

SILVER CROWN AREA - HANGINGWALL VEIN

<u>Hole No.</u>	<u>Cross Section</u>	<u>Vein Interval (m)</u>	<u>Thickness (m, true)</u>	<u>Assays (oz/ton)</u>	
				<u>Au</u>	<u>Ag</u>
SC91-17	8470N	20.12-20.66	0.97	13.68	229.7
SC91-18	8350N	30.72-31.70	0.96	0.20	1.4
SC94-1	8500N	29.15-30.48*	1.31	4.08	3.1
SC94-2	8530N	27.20-27.55	0.35	2.98	6.5
SC94-11	8500N	47.20-49.20	1.73	3.46	26.4
SC94-12	8470N	60.00-62.05 incl. 60.00-61.20	1.86 1.09	7.75 12.93	5.1 6.5
SC94-13	8440N	63.10-72.90 incl. 63.10-65.85	8.31 2.33	3.77 12.00	25.7 79.2
SC94-14	8440N	33.70-34.00 and 39.70-41.40	0.26 1.55	78.24(VG) 0.89	127.2 2.1
SC94-15	8410N	23.90-26.20	2.17	1.44	12.0
SC94-16	8410N	70.30-73.30	2.60	16.18(VG)	84.7
SC94-17	8380N	44.20-44.80	0.54	0.21	2.1
SC94-18	8410N	Faulted; fragments		-----	----
SC94-19	8440N	87.20-89.30(F)	1.84	2.33	38.1
SC94-20	8470N	80.80-92.40 incl. 88.20-91.60	9.73 2.65	1.75 4.35(VG)	4.1 6.9
SC94-21	8500N	78.00-84.80	5.89	0.45	6.2
SC94-22	8500N	97.50-102.40	3.28	0.93	2.1
SC94-23	8530N	47.40-51.90 incl. 48.30-48.80	3.90 0.43	2.19 16.42	35.7 276.3
SC94-24	8530N	83.80-87.30	2.87	0.60	2.4
SC94-25	8470N	104.60-105.90	0.92	0.03	2.7
SC94-26	8500N	In casing	----	-----	----
SC94-27	8500N	38.70-40.50	1.66	6.03	68.2

TABLE 2 (cont.)

Hole No.	Cross Section	Vein Interval (m)	Thickness (m, true)	Assays (oz/ton)	
				Au	Ag
SC94-28	8350N	Faulted out	----	-----	----
SC94-29	8410N	61.50-62.50(F)	0.88	0.89	6.2
SC94-30	8440N	In casing, and 11.30-13.30	---- 1.89	----- 7.54	---- 4.5
SC94-31	8440N	47.00-47.30 and 52.70-54.40	0.27 1.44	5.59 10.22	2.7 63.4
SC94-32	8500N	11.80-12.00	0.19	3.43	12.7
SC94-33	8470N	43.50-44.50	0.90	2.23	31.5
SC94-34	8455N	64.10-66.80 and 74.30-75.20	2.34 0.78	3.84 1.51	48.0 17.8
SC94-35	8440N	69.10-73.00 incl. 69.50-70.60 and 77.60-81.70	3.47 0.98 3.85	3.70 9.09 1.20	32.6 42.2 13.4
SC94-36	8425N	67.80-70.10 incl. 68.90-69.40	1.93 0.42	68.57 302.63(VG)	44.2 156.3
SC94-37	8530N	In casing	----	-----	----
SC94-38	8515N	23.70-24.20(F)	0.47	0.17	2.7
SC94-39	8425N	50.60-51.20(F)	0.54	3.53	41.8
SC94-40	8425N	76.20-80.70(Zone)	3.82	2.02(VG)	2.7
SC94-41	8485N	28.50-29.10(F)	0.52	7.82	2.7

* Interval includes 1.00 metre of pyritic hangingwall to vein.
(F) Interval faulted.

TABLE 3

DRILL HOLE INTERSECTIONSSILVER CROWN AREA - MAIN VEIN

<u>Hole No.</u>	<u>Cross Section</u>	<u>Vein Interval (m)</u>	<u>Thickness (m, true)</u>	<u>Assays (oz/ton)</u>	
				<u>Au</u>	<u>Ag</u>
SC91-17	8470N	46.66-48.01	1.31	0.14	3.8
SC91-18	8350N	61.07-61.37*	0.30	0.14	3.4
SC94-1	8500N	53.95-56.70** incl. 54.60-55.70	2.57 0.99	215.52 529.94 (VG)	80.6 172.8
SC94-2	8530N	55.70-57.80 incl. 55.70-56.90	1.90 1.09	6.24 10.08	65.1 99.8
SC94-11	8500N	82.00-83.30	1.15	4.49	79.5
SC94-12	8470N	92.00-96.80	4.07	0.48	8.6
SC94-13	8440N	93.10-99.70*+ incl. 96.00-97.10	5.65 0.94	2.43 10.11	8.2 35.0
SC94-14	8440N	58.90-61.20	2.05	4.83	41.5
SC94-15	8410N	62.30-63.10	0.79	5.01	10.3
SC94-16	8410N	95.60-98.50	2.65	3.57	26.7
SC94-17	8380N	83.40-84.70	1.19	0.08	1.0
SC94-18	8410N	Faulted out	----	-----	----
SC94-19	8440N	115.30-115.70 (F)	0.36	0.07	1.7
SC94-20	8470N	Dyked out	----	-----	----
SC94-21	8500N	Dyked out	----	-----	----
SC94-22	8500N	Dyked out	----	-----	----
SC94-23	8530N	82.20-82.30 (F)	0.09	0.24	6.2
SC94-24	8530N	113.80-115.60	1.47	5.93	9.6
SC94-25	8470N	138.70-139.20	0.38	0.14	1.0
SC94-26	8500N	21.30-24.00	2.10	1.78	25.4
SC94-27	8500N	72.00-73.60	1.37	6.00	45.3
SC94-28	8350N	96.60-97.20 (F)	0.53	0.17	5.8

TABLE 3 (cont.)

Hole No.	Cross Section	Vein Interval (m)	Thickness (m, true)	Assays (oz/ton)	
				Au	Ag
SC94-29	8410N	79.30-81.40	2.07	1.17	15.1
SC94-30	8440N	29.00-29.70	0.66	4.29(VG)	27.1
SC94-31	8440N	80.30-82.10	1.49	0.89	21.3
SC94-32	8500N	33.10-34.10	0.87	1.10	3.8
SC94-33	8470N	68.10-71.60 incl. 69.20-69.70	3.06 0.44	3.87 21.70(VG)	31.5 5.12
SC94-34	8455N	98.00-99.00	0.87	1.23	32.6
SC94-35	8440N	100.90-103.70(F)	2.42	0.03	1.0
SC94-36	8425N	93.00-95.40	2.12	3.43	13.7
SC94-37	8530N	24.40-25.60 incl. 24.40-24.80	1.12 0.37	13.03 30.31	7.5 13.7
SC94-38	8515N	54.30-55.30 incl. 54.80-55.30	0.96 0.48	44.60 87.74	64.8 121.7
SC94-39	8425N	75.40-76.80 incl. 75.90-76.80	1.27 0.82	13.92 21.12	20.9 31.9
SC94-40	8425N	105.80-106.10	0.28	0.21	1.0
SC94-41	8485N	53.90-54.30	0.35	0.86	2.7

- * Interval includes 0.15m of wallrock.
- ** Interval includes 0.65 metre of pyritic hangingwall to vein.
- *+ Interval includes 1.00 metre of pyritic hangingwall to vein.
- (F) Interval faulted.

REFERENCES

- Bostock, H.S. (1940): Keremeos; Geological Survey of Canada, Map 342A.
- Hassard, F.R. (1994): Diamond Drilling Report, Fairview Project (Brown Bear, Silver Crown and Winder 2 Mineral Claims); unpublished report for Oliver Gold Corp.
- Irvine, W.T. (1960): Fairview Property Review; Cominco Ltd., unpublished summary report.
- Little, H.W. (1961): Geology of the Kettle River (west half), British Columbia; Geological Survey of Canada Map 15-1961, scale 1:253,440.
- Mader, V., Lewis, P., and Russell, J.K. (1989): Geology and Structure of the Kobau Group between Oliver and Cawston, British Columbia: with Notes on Some Auriferous Quartz Veins; B.C. Ministry of Energy, Mines and Petroleum Resources, Geological Fieldwork 1988, Paper 1989-1, pp 19-25.
- Mehner, D.T. (1986): Geology, Fairview Property; unpublished set of geological maps (1:2,500) prepared for Oliver Gold Corp.
- Okulitch, A.V. (1969): Geology of Mount Kobau; unpublished Ph.D. Thesis, University of British Columbia, 141 pp.
- _____ (1973): Age and Correlation of the Kobau Group, Mount Kobau, British Columbia; Canadian Journal of Earth Sciences, Vol. 10, pp 1508-1518.
- Swanson, C.O. (1950): Fairview Mine Report; Cominco Ltd., unpublished summary report.
- Tupper, D.W. (1991): Diamond Drilling Report on the Brown Bear, Silver Crown, Ontario and Morning Star Claims, Fairview Project; unpublished report for Oliver Gold Corp.
- Wiley, W.E. (1982): Property Review, Fairview Belt; Cominco Ltd., unpublished summary report.

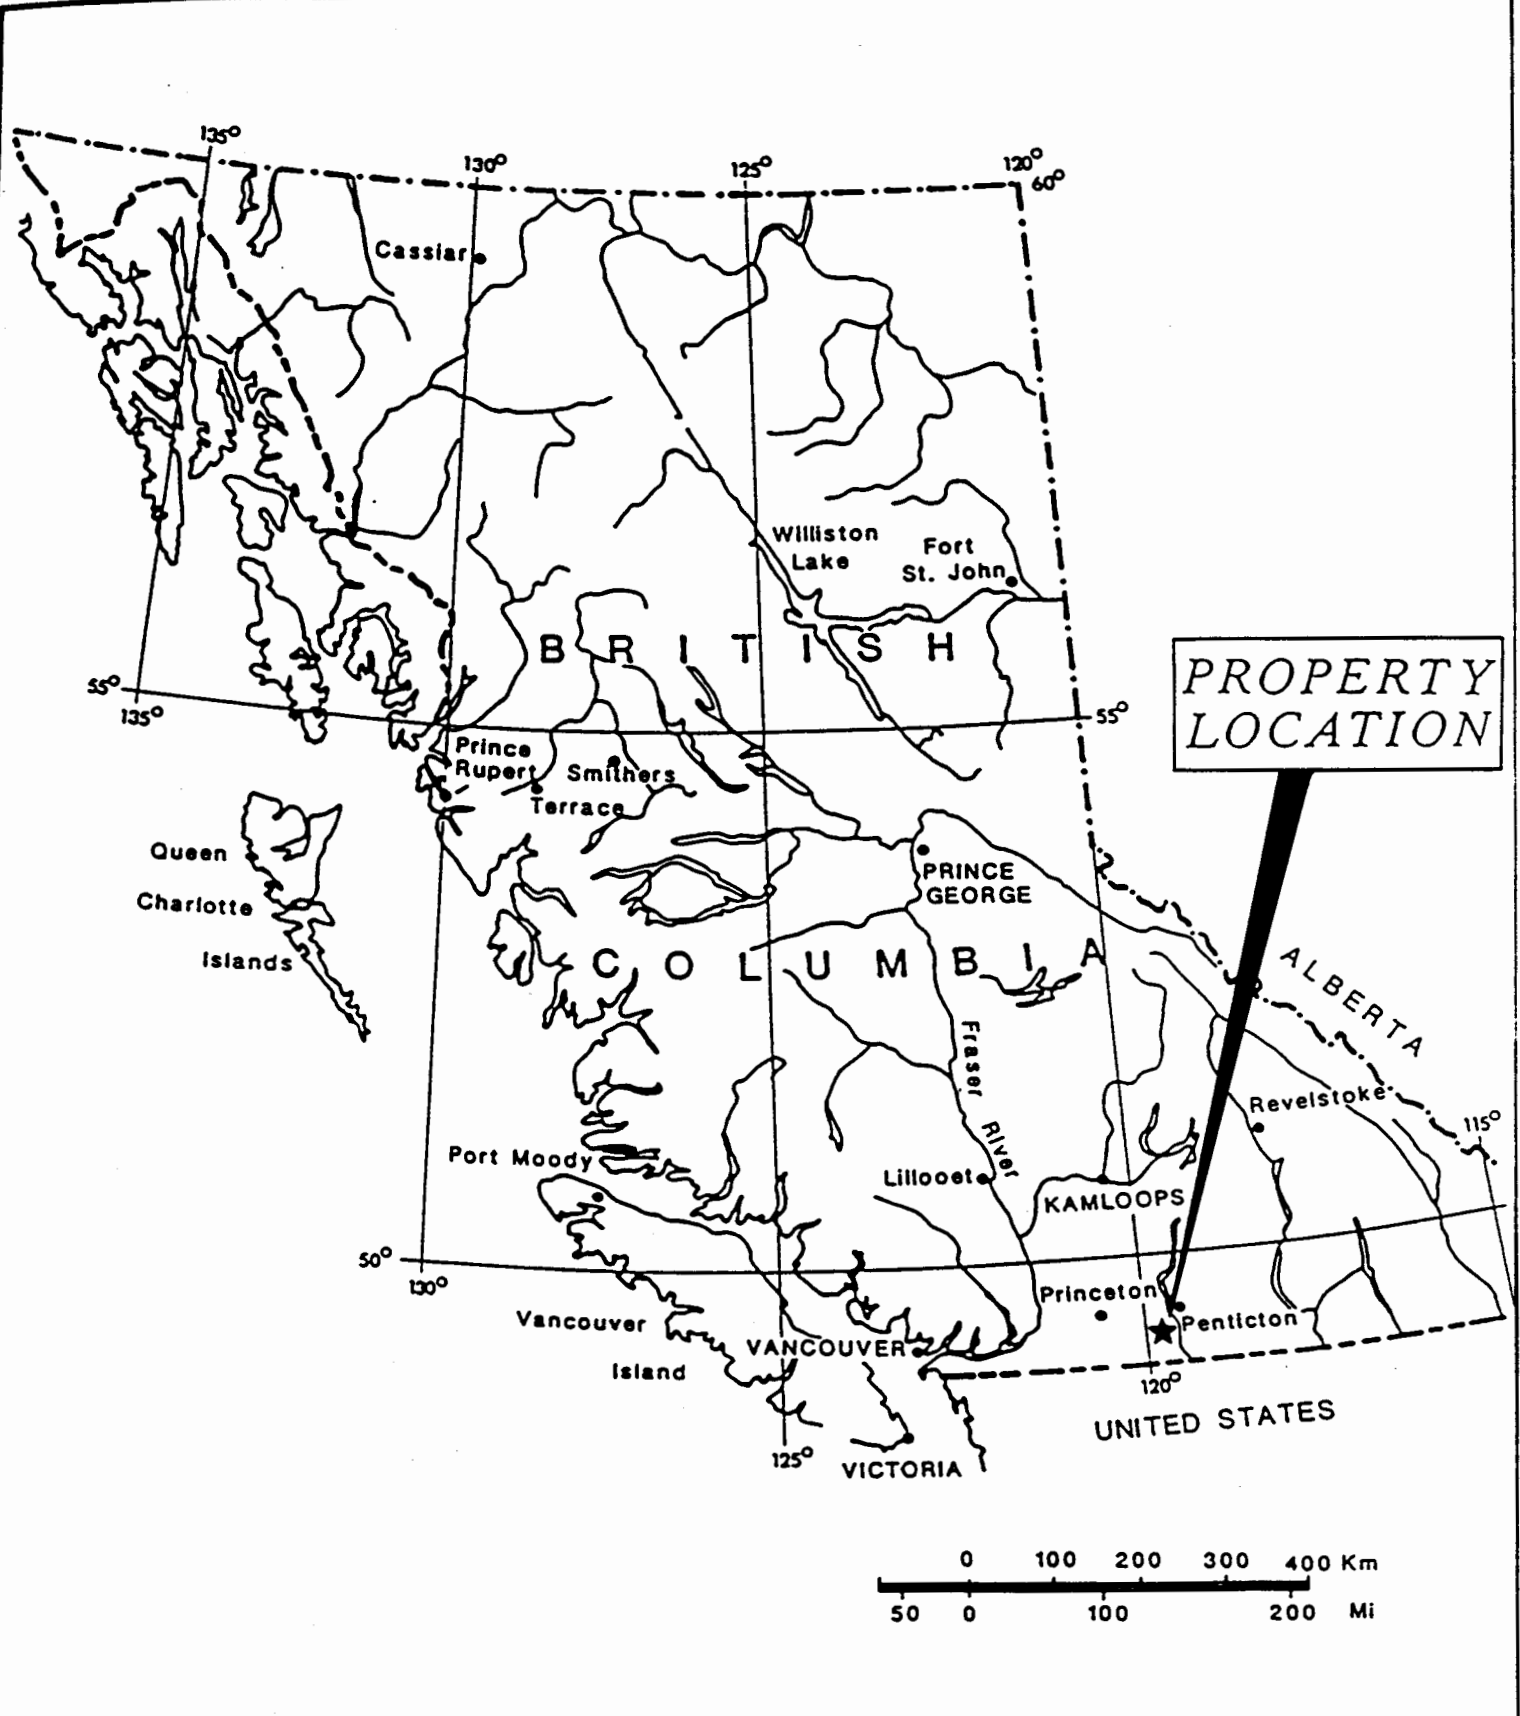


Figure 1
PROPERTY LOCATION MAP


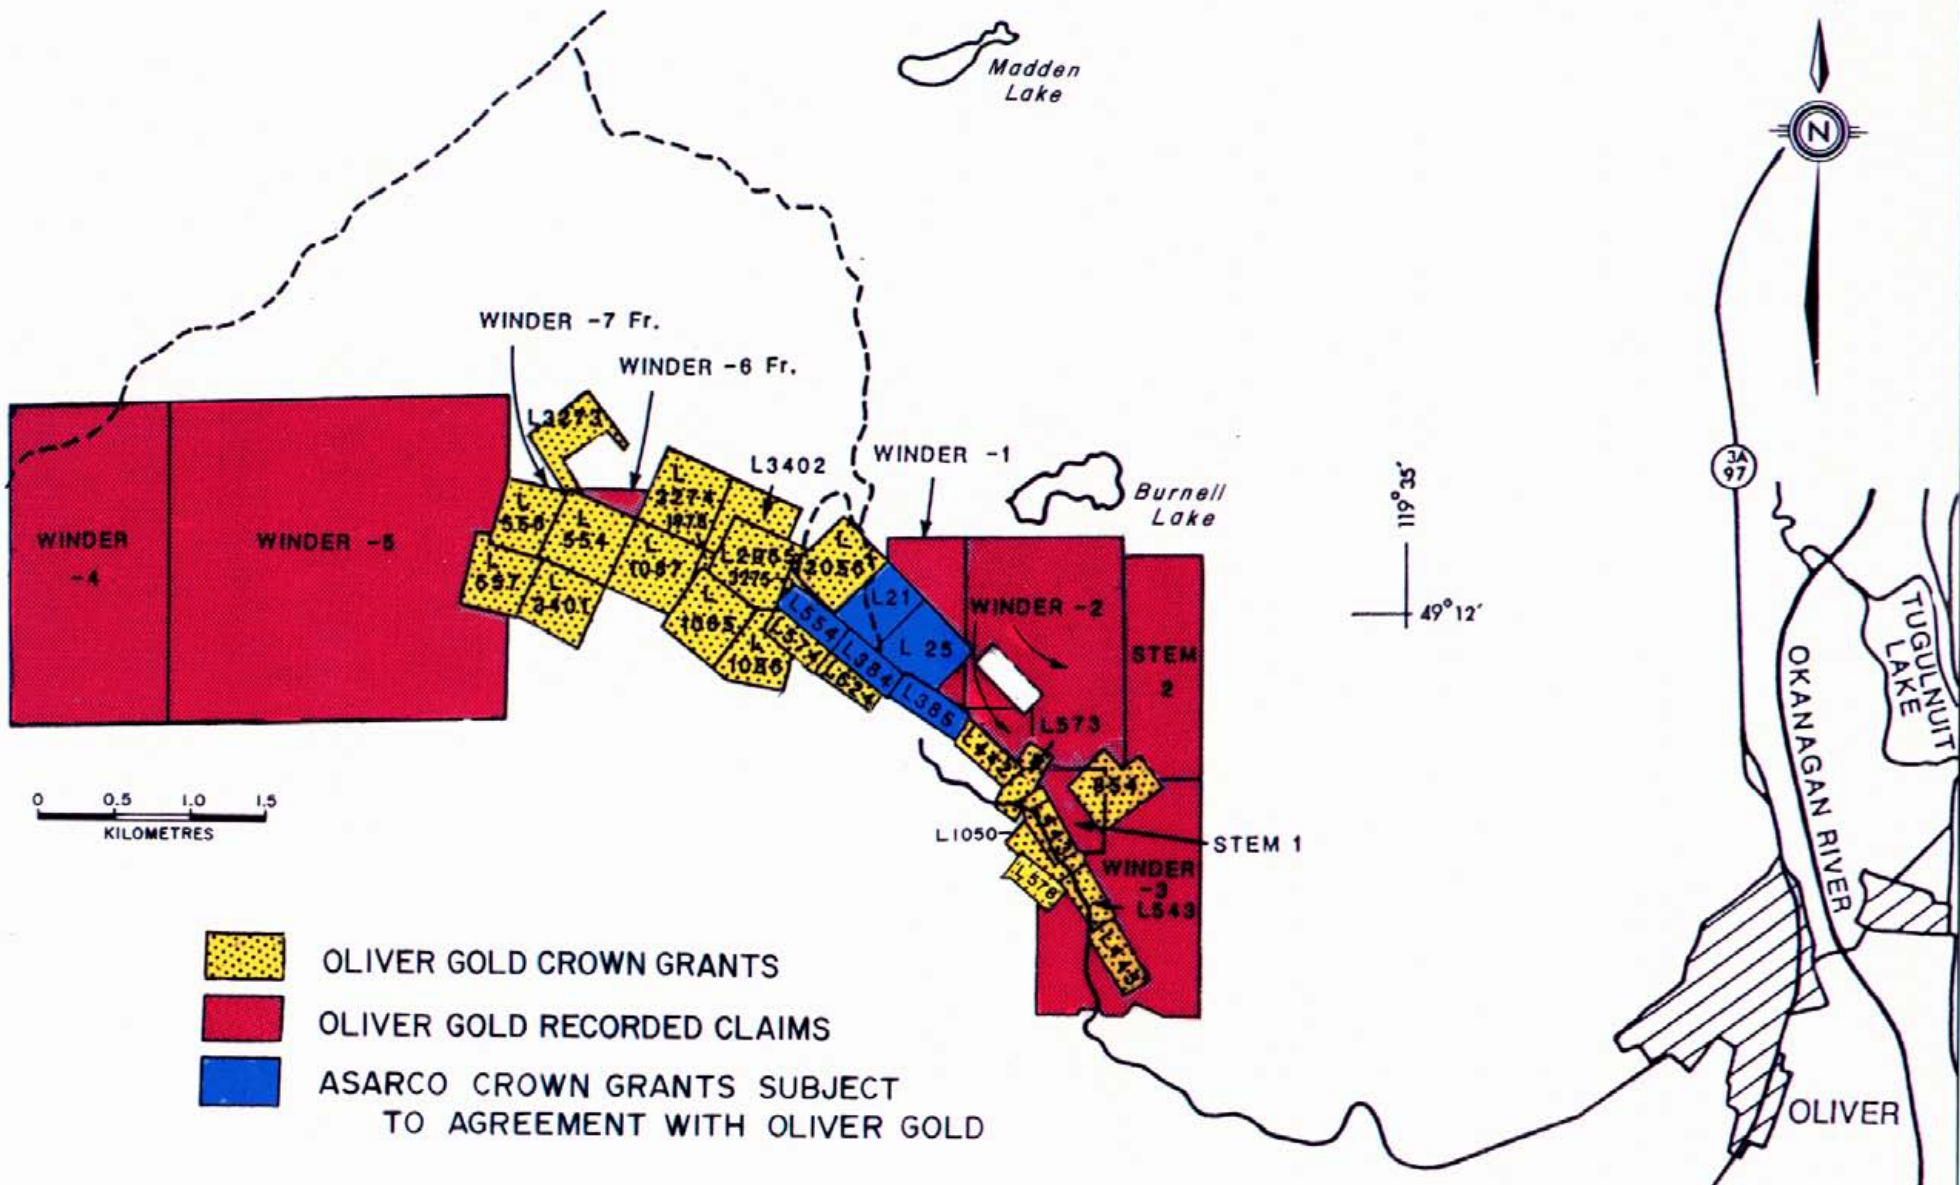


Figure 2

FAIRVIEW CROWN GRANTS AND MINERAL CLAIMS

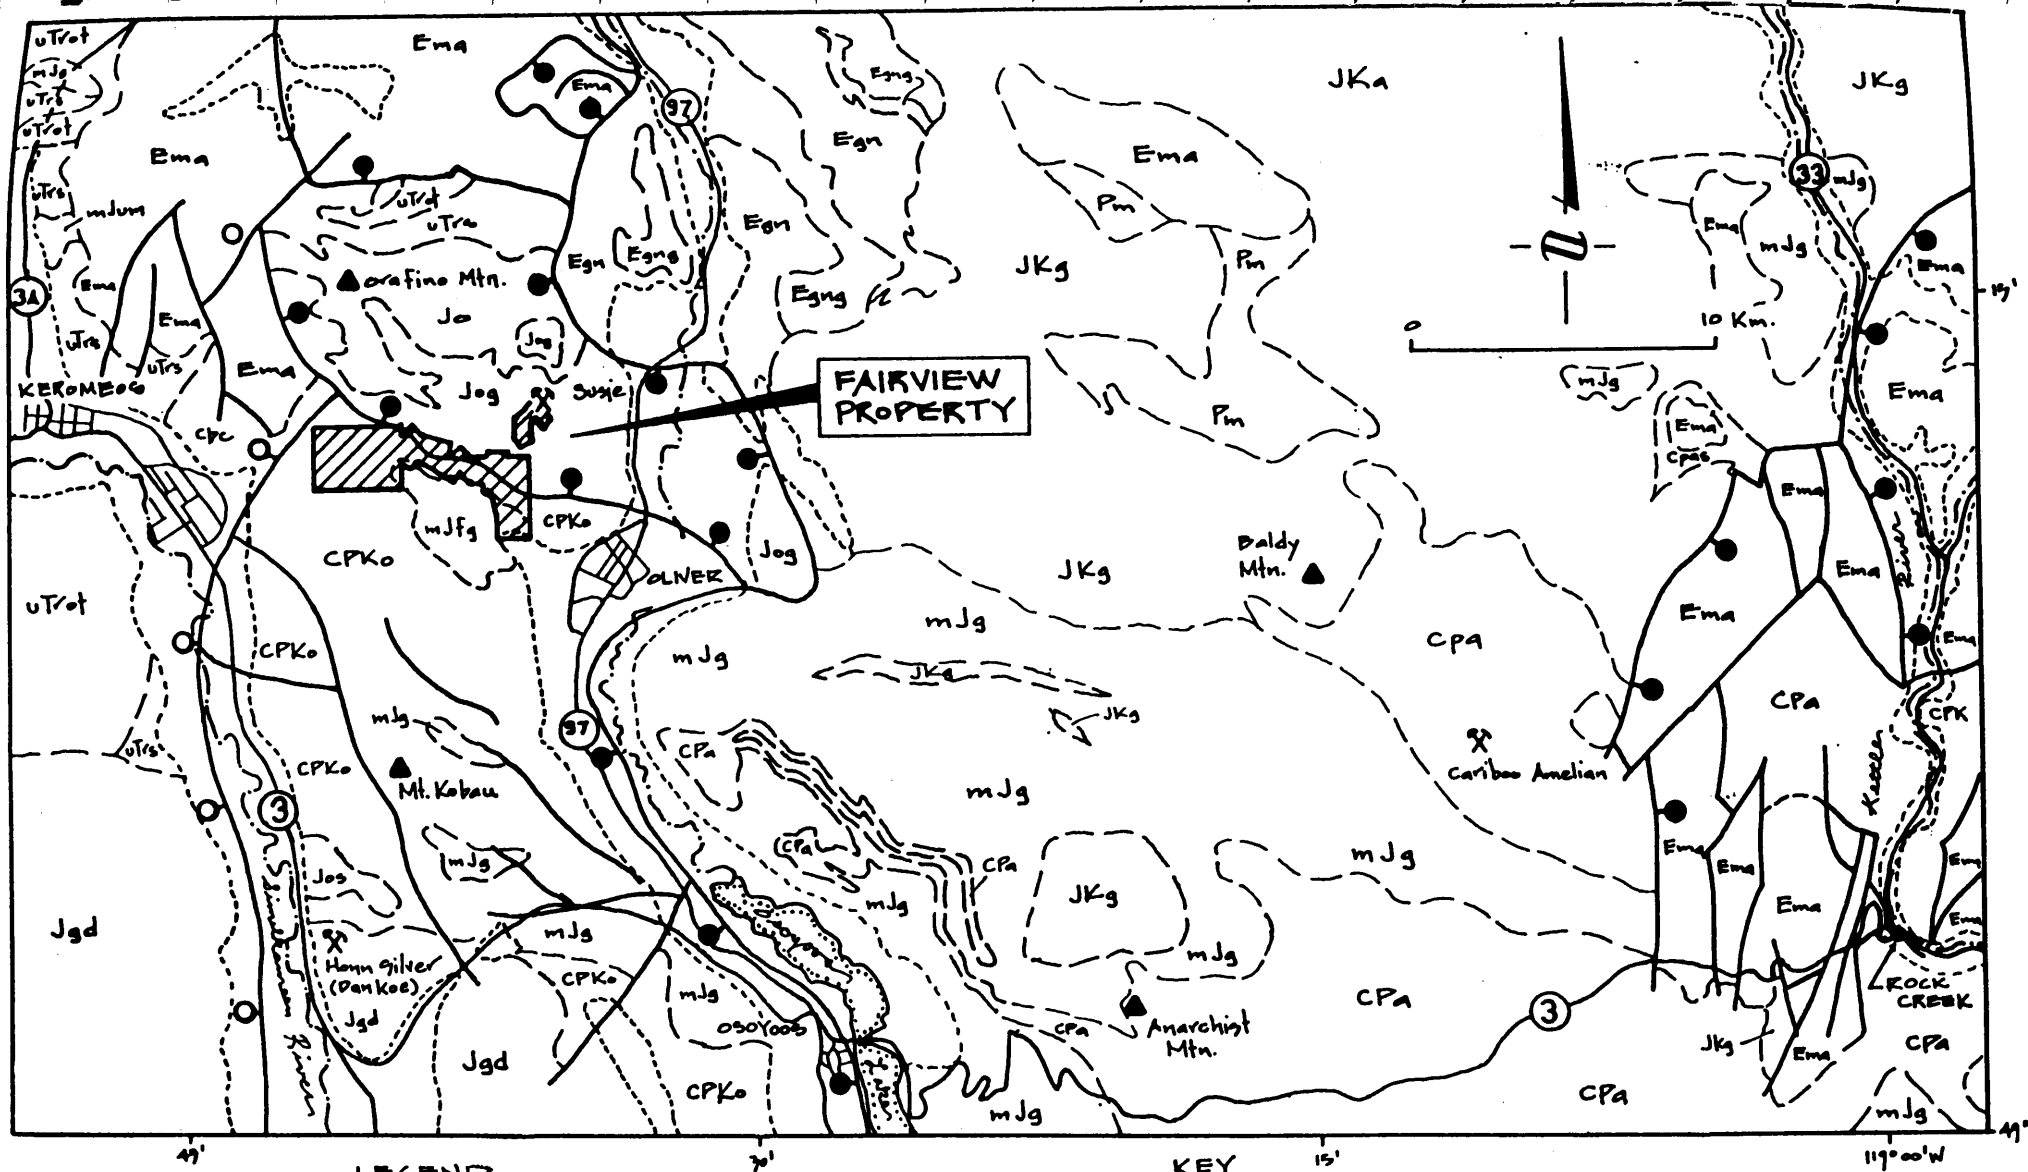

• EOCENE

Ema Marrou Group (undivided)
 Egn Okanagan gneiss
 Egn-g biotite granite gneiss

• CRETACEOUS and/or JURASSIC

JKg Okanagan Batholith
 Jo Oliver Pluton
 Jog - granite, Jod - diorite

• MIDDLE JURASSIC

mJg Nelson Plutonic Rocks
 mJfg Fairview Granodiorite

mJum Olalla Pyroxenite
 Jos Osyoos hornblende granodiorite

• ORDOVICIAN to LOWER JURASSIC

uTrot Old Tom Formation
 uTrs Shoemaker Formation

• CARBONIFEROUS or PERMIAN

CPK Knob Hill Group
 CPA Anarchist Group
 CPKo Kobau Group

• PROEROZOIC (?) / PALEOZOIC (?)

Pm Monashee Gneiss

--- Probable stratigraphic contact

--- Surficial deposit

--- Inferred fault movement/age unknown

♀ Inferred normal fault circle on downthrown side/age unknown

• Inferred Eocene normal fault, dot on downthrown side

⌘ Past producing Au-Ag mine

LEGEND

KEY

Figure 3
 OLIVER GOLD CORPORATION
 FAIRVIEW PROPERTY
 REGIONAL GEOLOGY

1:250,000

(After GSC Open File No 1909, 1989)

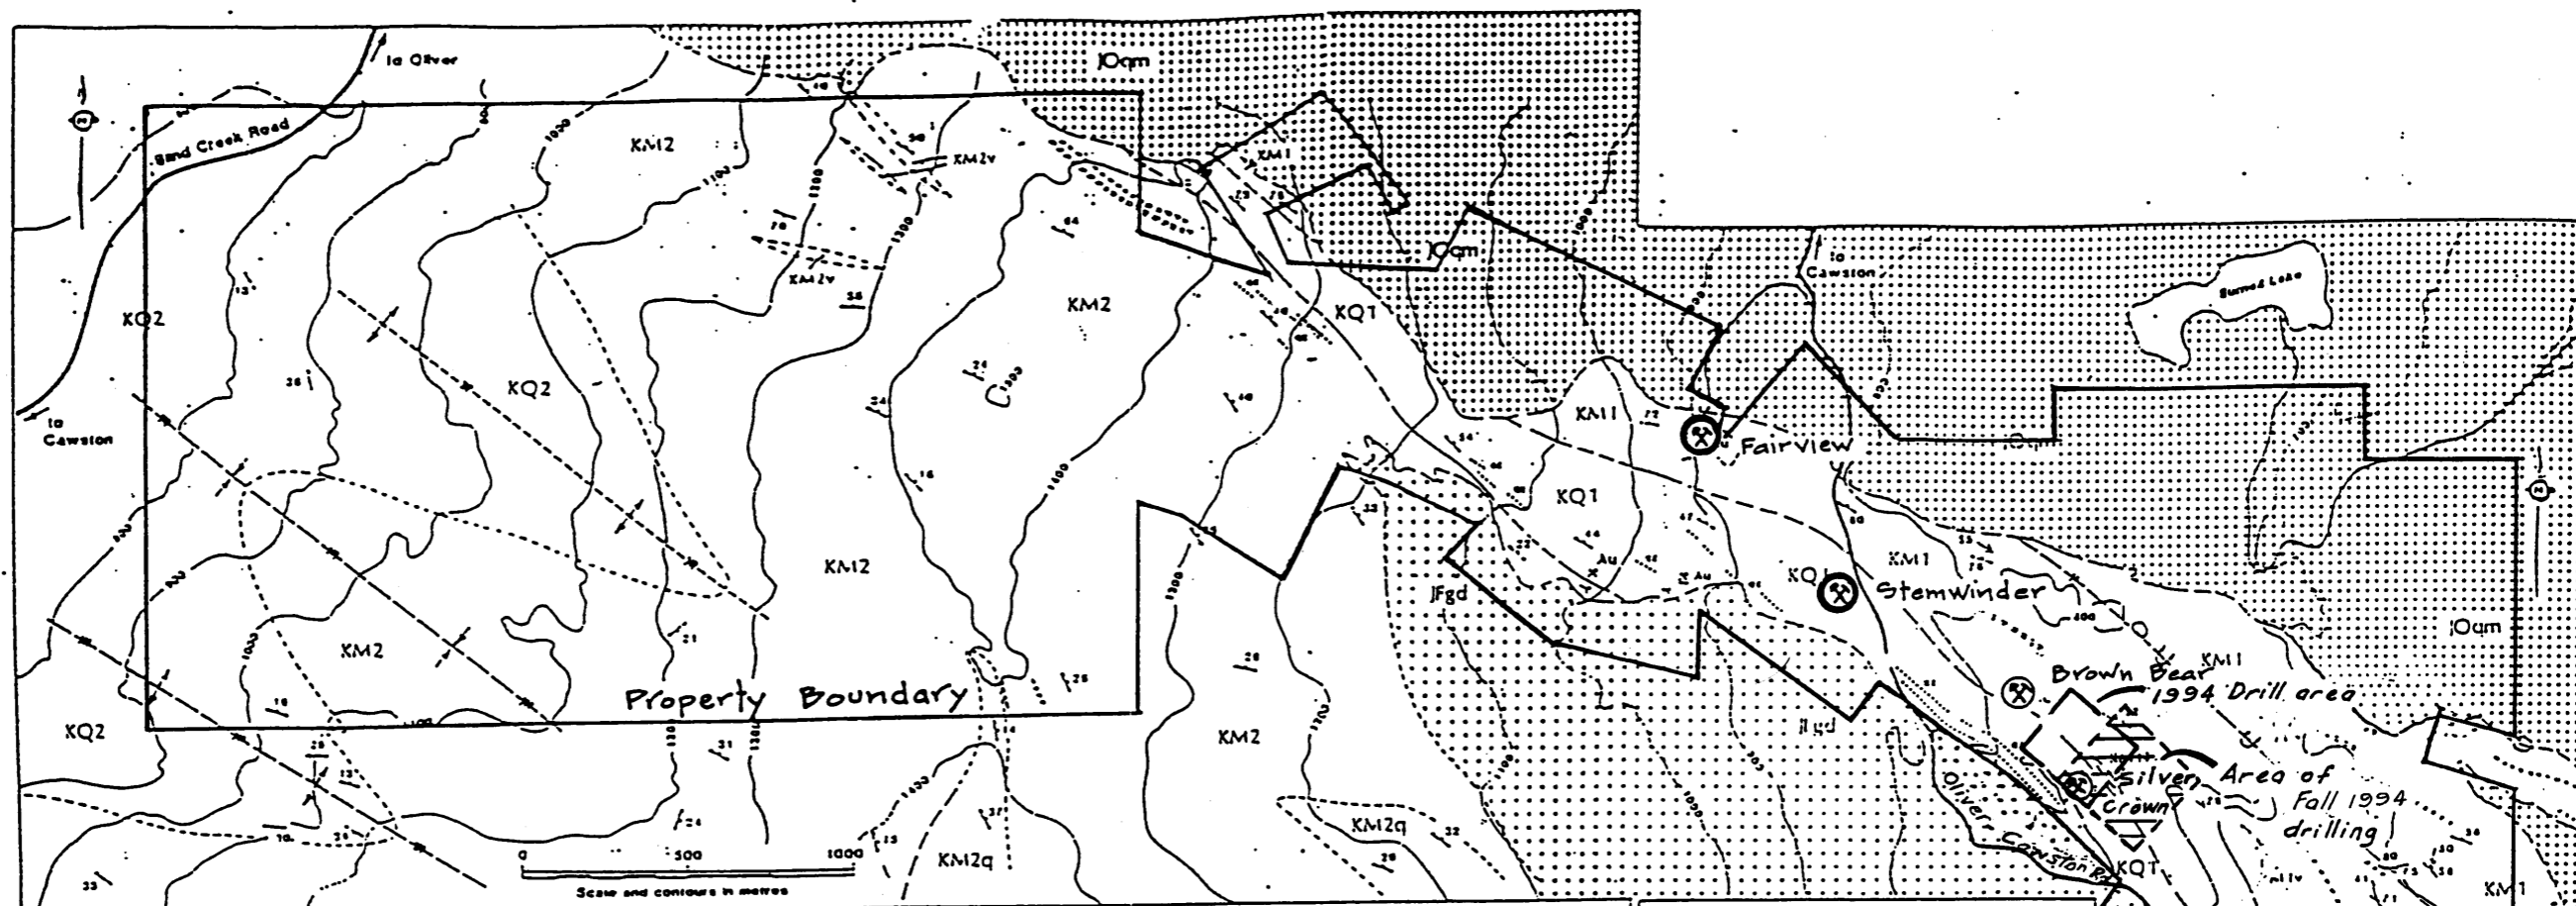


TABLE OF FORMATIONS

Period	Formation	Lithology
Tertiary, ca. 50 Ma	Mafic dykes	Prophyritic mafic dykes (augite, plagioclase, hornblende, biotite); some aphyric.
Jurassic(?)	Auriferous quartz veins	Veins near the Oliver pluton; generally massive, jointed, some ribbing; sulphide-poor; age relative to Fairview intrusion unknown.
Jurassic	Granitic, dioritic dykes and stocks	Aplite, aplitic granite, minor diorite and hornblende diorite; dykes and small stocks bordering the Oliver pluton or within Kohau Group rocks.
Jurassic, ca. 155 Ma	Oliver pluton (JQpm)	Complex, multiphase intrusion; K-feldspar-phryic quartz monzonite, granite and minor syenite; locally foliated border facies; locally agmatitic margin.
Jurassic(?)	Auriferous quartz veins (KQ2)	Vein systems along Fairview intrusion; sulphide-poor, locally containing pyrite, galena, sphalerite, chalcopyrite, graphite; commonly ribboned.
Jurassic(?)	Fairview granodiorite (JFgd)	Weakly foliated hornblende-bearing biotite granodiorite with minor granite and diorite; chlorite alteration common.
Pre-early Jurassic	Dacitic dykes	Plagioclase-quartz-phryic biotite dacite or plagioclase weakly foliated; 0.5-10 m thick; low-grade metamorphic overprint.
Pre-Jurassic		Polyphase deformation and metamorphism.

Period	Formation	Lithology
Pre-Jurassic	Kohau Group (KM1)	Types unknown, listed from east to west. Mafic schist 1: Alternate mafic layers (actinolite, biotite, epidote, minor feldspar, quartz, chlorite) and quartzite or feldspathic layers (actinolite, biotite, epidote, sphene, calcite, white mica (mm-cm)); some carbonate-rich sections (calcite, tremolite, epidote, feldspar, quartz); sections of quartz-feldspar-biotite schist; alternate biotite-rich (feldspar, quartz, epidote) and quartz-feldspar-rich (minor biotite, calcite) layers (mm-cm); lenses (1-50 m) of layered, foliated quartzite with thin biotite-rich laminae; boudins of massive quartzite; sections of uniformly mafic composition (10-100 m); calcite-marble boudins (2-15 m); rare lenses of augite-porphyrific mafic meta-volcanic flows or sills (relict augite, actinolite-chlorite-epidote matrix).
	(KQ1)	Quartzite 1: Quartzite layers (1-5 cm) separated by biotite-rich layers (mm-cm), foliated; some biotite-rich sections; lenses of mafic schist.
	(KM2)	Mafic schist 2: Similar lithologies as in mafic schist 1; black, foliated biotite-quartzite; lenses of mafic meta-volcanic flows or sills, coarse bedded, weakly foliated, primary textures obliterated; calcite marble (5-25 m) and minor calcite-tremolite marble.
	(KQ2)	Quartzite 2: Foliated quartzite with biotite-rich laminae, interbedded sections of mafic schist (1-20 m).

LEGEND

INTRUSIVE ROCKS


- Kpm: Oliver pluton, quartz monzonite and related rocks
- qz: Quartz veins associated with Jurassic intrusions
- Jgd: Fairview granodiorite

KOHAU GROUP METASEDIMENTS (Age and age unknown)

- KM1: Mafic schist unit 1, with calcite marble and rare mafic flows or sills (KM1v)
- (KQ1): Banded quartzite unit 1
- KM2: Mafic schist unit 2 with calcite marble, mafic volcanic rocks (KM2v) and quartzite (KM2q)
- (KQ2): Banded to massive quartzite unit 2

SYMBOLS

- Geological contact (dotted, dashed, assumed)
- Antiform (overturned) } phase of deformation indicated by number of the map
- Synform } phase of deformation indicated by number of the map
- Sensitively (Phase 1)
- Asses planes of minor folds (phase 2 and phase 1) with fold axis and vergence indicated
- Ad: Add
- Mine (cont. active, abandoned)

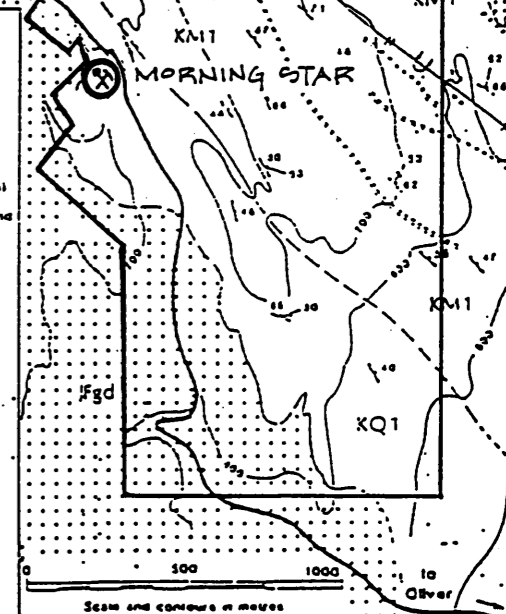

- (X) Mine (Abandoned)
- (X) Exploration Adit

Figure 4
OLIVER GOLD CORPORATION
FAIRVIEW PROPERTY
PROPERTY GEOLOGY
 1:2,500
 (After Mäder, 1987)

APPENDIX I

DRILL LOGS

DIAMOND DRILL HOLE LOG

LOCATION <u>SILVER CROWN</u>	HOLE NO. <u>SC94-14</u>
SECTION <u>8440N</u>	AZIMUTH <u>222°</u>
LATITUDE <u>8909.70N</u>	DIP <u>-60°</u>
DEPARTURE <u>11220.77E</u>	LENGTH <u>75.3m</u>
ELEVATION <u>743.32m</u>	PURPOSE <u>Test HWV & MV above 94-13</u>
CORE <u>NQ</u>	STARTED <u>Nov. 9, 1994</u>
LOGGED BY <u>F.A. Hayward</u>	COMPLETED <u>Nov. 10, 1994</u>

DIP TESTS

TEST	FOOTAGE			DIP	LATITUDE	DEPARTURE
	FROM	TO	TOTAL			
1	75.3m			-58°		

CLIENT OLIVER GOLD CORP
PROPERTY FAIRVIEW

METRES		DESCRIPTION	CORE SAMPLES							AVERAGES
FROM	TO		NUMBER	FROM (m)	TO (m)	WIDTH (m)	Au (OPT)	Ag (OPT)		
		STORAGE: Fairview Core Shack								
		HEIGHT OF CASING ABOVE GROUND: 0.3m								
0	3.0	CASING								
3.0	36.8	SERICITIC QUARTZITE (UNIT 3)								
		Light to medium grey, 3-8% fine-grained sericite; minor brownish or dark grey to greenish bands and short sections to 30 cm. with variable amounts of biotite and/or chlorite to 8%; trace fine-grained pyrite throughout. Minor quartz veinlets @ 5-15°. Foliation and compositional banding @ 65-75° to C.A.								
		(3.0 - 8.5) Limonite-stained fractures.								
		(19.0 - 19.8) Breccia. Medium grey to black fragments 1-10mm in 10% whitish to medium grey quartzose matrix, minor light grey quartz veinlets @ 5-10° to C.A. Minor graphitic slips @ 70-80°.								
		(19.8 - 25.0) Broken core, weakly to moderately sheared, sericitic slips and thin whitish clayey gouge @ 5-30° and 65-75° to C.A.								
		(26.4 - 29.0) Breccia and shear zone. Weakly to moderately brecciated with sections to 40cm of quartzite fragments 1mm to 5cm in clayey matrix mixed with sections of crackle breccia. Light to dark grey clayey gouge and fine breccia zones @ 30-70°. Gradational contacts.								
		(30.8 - 33.7) Weakly to moderately sheared, broken core as (19.8-25.0). Section ends at 0.5m sandy gouge and ground core.	50549	32.2	33.7	1.50	0.006	0.03		
		(33.7 - 34.0) QUARTZ VEIN - possible splay of Hanging Wall Vein White quartz with minor dark grey to black sericitic and graphitic bands near center of vein. Trace to 1% fine-grained galena and reddish-brown sphalerite along 1mm stylolitic fractures and veinlets @ 60-70°, minor fine-grained pyrite throughout, very fine <u>Visible Gold</u> at 33.9m. Broken contacts.	50550	33.7	34.0	0.30	2.282	3.71	** <u>Visible Gold</u>	
36.8	39.7	CHLORITIC, BIOTITIC QUARTZITE (UNIT 2)	50551	34.0	35.0	1.00	0.012	0.03		
		Medium to dark brown, locally dark greenish, 3-8% fine-grained biotite, locally minor chlorite, trace pyrite. Foliation and compositional banding @ 60-70°. Upper contact gradational over 20cm, lower contact sharp @ 85°.								
		(37.5) 5mm clayey gouge @ 35°; compositional banding locally subparallel to core.	50552	38.7	39.7	1.00	0.002	<0.02		

DIAMOND DRILL HOLE LOG

DIP TESTS									
TEST	FOOTAGE			DIP		LATITUDE		DEPARTURE	
	FROM	TO	TOTAL		CORR.	CUM		CUM	
1	78.0				-40°				

CLIENT OLIVER GOLD CORP.
PROPERTY FAIRVIEW

LOCATION WINDER 2 HOLE NO. SC94-15
SECTION 8410N AZIMUTH 222
LATITUDE 8886.57N DIP -45°
DEPARTURE 11240.23E LENGTH 78.0m
ELEVATION 744.01m PURPOSE Test HWV & MV
CORE NQ STARTED Nov. 10, 1994
LOGGED BY P. B. Haggard COMPLETED Nov. 11, 1994

METRES		DESCRIPTION	CORE SAMPLES							
FROM	TO		NUMBER	FROM	TO	WIDTH	Au	Ag	AVERAGES	
0	3.0	STORAGE: Fairview Core Shack ; HEIGHT OF CASING ABOVE GROUND: 0.3m CASING		(m)	(m)	(m)	(OPT)	(OPT)	Au, Ag - width (OPT) (m)	
3.0	14.6	BIOTITIC QUARTZITE (UNIT 2) Dark to medium greyish brown, locally greyish or greenish, with approx. 5% biotite + 1-2% sericite or chlorite, trace pyrite. Foliation and compositional banding @ 80°, becoming 65-70° down section. (8.1 - 8.3) Quartz vein, white and grey with limonite-stained fractures. Contacts @ 80°. Trace pyrite. (11.4 - 14.6) Grey and brownish, slightly bleached, gradational lower contact. Scattered quartz veinlets and small veins to 2cm. Veinlets and stringers generally subparallel to core; small veins irregular @ 60-70° to C.A.								
14.6	18.4	FAULT ZONE Light grey section of crushed, locally brecciated sericitic quartzite with numerous thin clayey gouges @ variable angles and thin vuggy white quartz veinlets. Upper contact sharp at 1-3cm gouge @ 70°; lower contact sharp at 1cm gouge @ 70°.								
18.4	23.9	BIOTITIC QUARTZITE (UNIT 2) Brownish to dark grey, similar to (3.0 - 14.6). Lower 60 cm is medium to dark grey, siliceous and somewhat broken to coarsely fragmental. Lower contact sharp @ 70°.	50561	22.9	23.9	1.00	0.002	<0.02		
23.9	26.2	QUARTZ VEIN (Hanging Wall Vein) White to grey quartz, streaked and banded with dark grey to black. Contains 20% silicified foliated sericitic quartzite as 1 to 20 cm sections scattered throughout. 1-3% pyrite as fine grains, trace very fine to fine-grained galena and reddish-brown sphalerite, widely disseminated and in narrow bands subparallel to the general foliation. Scattered graphitic slips. Upper contact sharp along graphitic slip @ 70°; lower contact broken at narrow sandy gouge @ 60°.	50562	23.9	25.0	1.1	0.080	0.62		
			50563	25.0	26.2	1.2	0.008	0.10	0.042, 0.35 - 2.3	
26.2	42.3	SERICITIC QUARTZITE (UNIT 3) Medium grey, locally light grey or dark greenish grey, trace to 1% pyrite. Upper part to about 37m has numerous broken sections, clayey to sandy gouge, minor graphitic slips and scattered vuggy white quartz veinlets @ variable low angles to C.A. Below 37m, section is much less tectonized, regularly foliated @ 70-75°. Lower contact sharp but irregular.	50564	26.2	27.2	1.0	<0.001	<0.02		

DIAMOND DRILL HOLE LOG

FOOTAGE				DIP TESTS		LATITUDE		DEPARTURE	
TEST	FROM	TO	TOTAL	DIP	CORR.	CUM		CUM	
1				-56°					
2				-55°					

CLIENT OLIVER GOLD CORP.
PROPERTY FAIRVIEW

LOCATION WINDER 2 HOLE NO. SC94 - 16
SECTION 8410N AZIMUTH 222°
LATITUDE 8914.61N DIP -63°
DEPARTURE 11265.84E LENGTH 110.0m
ELEVATION 742.81m PURPOSE Test HWV & MV
CORE NO. STARTED Nov. 11, 1994
LOGGED BY P.R. Hassard COMPLETED Nov. 13, 1994

METRES		DESCRIPTION	CORE SAMPLES						AVERAGES
FROM	TO		NUMBER	FROM	TO	WIDTH	Au	Ag	
		STORAGE: Fairview Core Shack		(m)	(m)	(m)	(OPT)	(OPT)	
		HEIGHT OF CASING ABOVE GROUND: 0.3m							
0	3.0	CASING							
3.0	19.5	BIOTITIC QUARTZITE (UNIT 2)							
		Medium grey streaked and finely banded with medium brown, dark grey and greenish grey. Banding @ 70-80°, few minor fractures. Contains about 5% fine-grained biotite, 1-2% sericite and locally 1-2% chlorite, trace pyrite. Lower contact gradational over 20 cm.							
		(13.2 - 13.5) Light to medium grey alteration about central graphitic slip @ 75°.							
19.5	28.0	SERICITIC QUARTZITE (UNIT 3)							
		Light to medium grey, banded with medium grey to pale brown. About half the section is broken with sections of fractured quartzite with thin clayey slips up to 1.5m long. Similar to (3.0 - 19.5) except sericite is most abundant mica to about 5%, with 1-2% slightly altered biotite locally. Lower contact gradational over 1m.							
		(22.0 - 22.5) Broken core, several thin whitish clayey slips at indeterminate attitudes; 5mm dark grey clayey gouge subparallel to core in upper 0.5m.							
		(25.5) 1cm whitish clayey, sandy gouge @ 80°.							
28.0	64.2	BIOTITIC QUARTZITE (UNIT 2)							
		Similar to (3.0 - 19.5). Below about 52.5, biotite generally decreases and sericite increases to about 50:50 in general; short 10-30cm sections of sericitic quartzite occur; minor short chloritic sections. Few broken zones.							
		(38.9 - 39.0) 8 cm white quartz vein, 1-2% fine- to medium-grained pyrite, 2-3% fine-grained galena, disseminated along a central band and as aggregates, trace to 1% reddish-brown sphalerite, trace chalcopyrite. Contacts sharp @ 55-65°	50571	38.8	39.1	0.3	0.132	0.77	
		(49.7 - 51.0) 5cm bluish-grey quartz vein subparallel to core. Cut by occasional fractures @ 15-20° with trace pyrite on fracture planes.							
		(61.3 - 61.6) Fault; 2-5cm whitish and black clayey and locally graphitic gouges @ 70-80°; 20cm breccia of 20% medium grey quartzite fragments in clayey quartzose matrix.							

METRES		DESCRIPTION	CORE SAMPLES								
FROM	TO		NUMBER	FROM	TO	WIDTH	Au	Ag	Au**	AVERAGES	
		(63.5) 10cm broken graphitic fragments. Graphitic slips @ 80°.		(m)	(m)	(m)	(OPT)	(OPT)	(OPT)	** Screened for metallics	Au, Ag - width (OPT) (m)
64.2	70.3	SERICITIC QUARTZITE (UNIT 3) Similar to (19.5 - 28.0), minor short broken sections. Foliation generally @ 70-80°. Minor thin quartz veinlets, occasionally slightly sheared or vuggy. @ 10-30°. Lower contact sharp but irregular.									
		(68.1) 3cm slightly graphitic sandy gouge and fragments @ 65°.									
		(69.3 - 69.8) Broken core, fractures @ 70 - 80° and 40°.	50572	69.3	70.3	1.0	0.001	<0.02			
		(69.8 - 70.3) Numerous quartz veinlets to 2mm @ 10-20°. Lower 10 cm contains pale greenish altered micas along foliation @ 75-80°.									
70.3	73.3	QUARTZ VEIN (Hanging Wall Vein) (70.3 - 71.2) 10cm white quartz followed by 70-80cm broken vein quartz and quartzite wall rock, numerous graphitic slips; section ends at 2-3cm sandy graphitic gouge @ 60°. Minor pyrite. 70% recovery.	50573	70.3	71.2	0.9	0.002	0.11			
		(71.2 - 72.6) White vein quartz with about 30% whitish bleached quartzite as short crushed sections from 71.6 - 72.0m. Graphitic slips and gouge @ 75-80° in lower 30 cm. 60% recovery.	50574	71.2	72.6	1.4	0.043	0.80			0.472, 2.47 - 3.0
		(72.6 - 73.3) White vein quartz with scattered graphitic slips. Lower 40cm quite broken; 70-80% recovery. Disseminated pyrite throughout. Upper 30cm contains 1-3% disseminated galena and 1% reddish-brown sphalerite, 1-2% chalcopyrite in blebs and irregular masses to 3mm; very fine grains of native Gold at 72.9m. Minor sulphides in lower 40 cm. Lower contact broken.	50575	72.6	73.3	0.7	2.038	8.85	1.935		
73.3	78.0	SERICITIC QUARTZITE (UNIT 3) As lower part of (64.2 - 70.3). Lower contact broken.									
		(73.3 - 74.1) Light to medium grey, locally streaked with black, slightly crushed with contorted foliation in upper 30cm. Graphitic slips @ 60-80°.	50576	73.3	74.3	1.0	0.006	0.03			
		(74.1 - 75.2) Broken core, 50% recovery.	50577	77.0	78.0	1.0	0.003	0.03			
78.0	79.8	QUARTZ VEIN (Hanging Wall Vein Splay) (78.0 - 78.5) White quartz streaked and mottled with grey or black. Fractures @ 20-35°, minor graphite. Trace pyrite. 70% recovery.	50578	78.0	78.5	0.5	0.085	0.40			
		(78.5 - 79.4) Broken quartz vein and graphitic fragments and gouge. Minor pyrite. 40% recovery.	50579	78.5	79.4	0.9	0.039	0.30			0.046, 0.32 - 1.8
		(79.4 - 79.8) Upper 20cm crushed altered quartzite, lower 20cm white vein quartz with minor pyrite. Lower contact at graphitic slip and 2cm clayey graphitic gouge @ 70-80°.	50580	79.4	79.8	0.4	0.013	0.25			

METRES		DESCRIPTION	CORE SAMPLES							AVERAGES			
FROM	TO		NUMBER	FROM	TO	WIDTH	Au	Ag					
				(m)	(m)	(m)	(OPT)	(OPT)					
79.8	85.0	SERICITIC QUARTZITE (UNIT 3) As (73.3 - 78.0). Short broken sections to 78.5m. (83.7 - 84.1) 5cm breccia with rounded grey fragments to 1cm, commonly 2-5mm, in dark grey matrix. Zone @ 30° to C.A., followed by broken core and 1-2cm clayey gouge near 84.0m. (84.8 - 85.0) Clayey and sandy gouge and small fragments. Zone @ 10-30° to C.A.	50581	79.8	80.8	1.0	0.002	<0.02					
85.0	95.6	CHLORITIC QUARTZITE (UNIT 2) Medium grey banded with dark grey, green and black. Foliation @ 80°. Trace pyrite. Upper contact sharp at gouge; lower contact sharp @ 40°. (89.7 - 90.2) Irregular quartz veinlets to 2mm, graphitic slips @ 20-40°. (90.4 - 90.7) Irregular quartz veinlets and masses to 1cm @ 10-20°. (91.7 - 92.3) Irregular quartz veins and fragments along slip @ 10-20°. Section ends at graphitic slip @ 40°. (92.5 - 94.5) Graphitic slips and contorted banding and foliation. Strong deformation at 93.6-94.5m @ 40°, 5cm quartz vein and graphitic fractures at 93.9 @ 40°. (94.5 - 95.6) Minor scattered graphitic slips, foliation @ 50°, trace pyrite.	50582	94.5	95.6	1.1	0.007	0.04					
95.6	98.5	QUARTZ VEIN (Main Vein) (95.6 - 96.3) 20cm white quartz cut by few creamy vuggy quartz veinlets @ 5-10°, trace pyrite; followed by 10cm sheared and quartz-veined sericitic quartzite. Contacts and shears @ 40°. Lower 40cm white vein quartz, broken, trace pyrite 80% recovery. (96.3 - 96.6) White quartz, 1-2% pyrite concentrated along a 3cm wide zone of bands @ 40° near end of section. 100% recovery. (96.6 - 97.2) White vein quartz, trace pyrite, galena and sphalerite as disseminated crystals and small 1-2mm aggregates. Broken core, 60% recovery. (97.2 - 98.1) White vein quartz, trace to 1% fine-grained pyrite, occasional aggregates to 1mm, trace very fine grained galena and reddish-brown sphalerite. Short broken sections, 80% recovery. (98.1 - 98.5) White vein quartz with graphitic slips and gouge increasing in thickness and frequency down section. Lower contact @ 1-2cm graphitic gouge. Weak banding in quartz vein @ 50°, slips and gouge @ 40°. 90% recovery.	50583	95.6	96.3	0.7	0.007	0.08					
			50584	96.3	97.2	0.9	0.204	1.39					0.104, 0.78 - 2.9
			50585	97.2	98.1	0.9	0.117	0.91					
			50586	98.1	98.5	0.4	0.018	0.34					
98.5	100.7	SERICITIC QUARTZITE (UNIT 3) Light to medium grey, "bleached" appearance, streaked and banded with medium grey @ 50°. Upper 1m has several short crushed and gouged sections. Grey clayey gouges to 1cm @ 40-80°. Lower contact gradational over 1m.	50587	98.5	99.5	1.0	0.001	<0.02					

METRES		DESCRIPTION	CORE SAMPLES										
FROM	TO		NUMBER	FROM	TO	WIDTH	Au	Ag					AVERAGES
			(m)	(m)	(m)	(OPT)	(OPT)						
44.8	53.9	CHLORITIC, BIOTITIC QUARTZITE (UNIT 2) Similar to (3.0 - 19.4); minor short bleached sections of sericitic quartzite to 20cm long. Foliation and banding @ 70-80°. Minor quartz veinlets and stringers @ 5-20°. Lower contact gradational over 50cm.	50590	44.8	45.8	1.0	0.003	0.04					
53.9	66.1	SERICITIC QUARTZITE (UNIT 3) Light to medium grey, streaked and banded with darker grey and locally tan @ 80°. Trace to 1% pyrite. (55.7 - 55.9) Fault. 2-3cm whitish and black clayey, sandy gouge, broken graphitic quartzite and 3mm zone of 1mm quartz veinlet, clay gouge and graphite @ 35-40°. (56.2 - 57.0) Siliceous, broken core, quartz stringers and contorted fractures @ 20-30°. (57.8 - 59.1) Vuggy, cream quartz vein to 1.5cm subparallel to core, small scale folds, quartz stringers and fractures. (59.1 - 61.0) Breccia and Fault Zone. Upper 90cm light grey matrix with 40% medium grey to black fragments 1-4mm and larger broken foliated sections a few cm long. Lower 1m is graphitic slips and 10-15cm crushed and gouge zones @ 50°. Upper contact sharp but irregular, lower contact along graphitic slip @ 60°. (61.0 - 64.7) Grey and light brown, foliated @ 65-70°. Slightly altered Biotitic Quartzite. (64.7 - 64.9) 10cm creamy and light bright green gouge @ 60°, followed by 10cm medium grey quartz vein, trace pyrite, @ 55°; sharp contacts. (64.9 - 65.5) Grey quartzite with black graphitic slips @ 60-70°. (65.5 - 66.1) Grey foliated @ 70-80°. Lower contact broken.											
66.1	73.0	FAULT ZONE Extremely broken, much sandy gouge and lost core (66.1 - 66.3) Broken, grey breccia with 40-60% fragments, 1-5mm in fine grey matrix 5cm barren quartz vein at end. (66.3 - 70.7) Broken, 10% recovery. Fragments of brecciated quartzite and sandy gouge, 10cm of medium grey sandy gouge with 5-10% white vein quartz fragments. (70.7 - 71.3) White quartz vein, graphitic gouge. 30% recovery. (71.3 - 72.8) Grey to tan fine-grained sand with small fragments of quartzite and white vein quartz containing about 1% pyrite. Quartzite fragments to 5mm; vein quartz to 6cmX2cmX3cm, fractured and crushed. 5% recovery. Water return contained much fine sand, grains of tan quartzite, which later flowed into the hole.	50591	68.9	70.7	1.8	0.020	0.13					
			50592	70.7	71.3	0.6	0.012	0.16					
			50593	71.3	72.8	1.5	0.002	0.06					

METRES		DESCRIPTION	CORE SAMPLES							AVERAGES Au, Ag - width (OPT) (m)
FROM	TO		NUMBER	FROM	TO	WIDTH	Au	Ag		
		(72.8 - 73.0) Siliceous conformed quartzite and grey quartz vein. Small seam of pyrite 1-2mm @ about 30°. Lower contact sharp on foliation @ 60°. 100% recovery.	50594	72.8	73.0	0.2	0.003	0.07		
73.0	83.4	CHLORITIC QUARTZITE (UNIT 2) Greyish banded with dark greenish-black. Minor white quartz stringers, trace pyrite. Upper 3m is medium greyish-green, altered, minor slips with chlorite and/or sericite. Foliation irregular. Minor graphitic slips. (76.4 - 77.1) Graphitic slips and minor broken quartz veinlets. Slips @ 40-50°. (78.3 - 79.6) Scattered graphitic slips @ 40°. (79.6 - 80.3) Quartz Vein. White and grey banded quartz, slightly vuggy in upper 20cm, numerous fine pyritic seams and masses, mainly in upper 30cm. Lower 30cm broken and graphitic with white quartz, trace pyrite and very fine grained galena. Contacts sharp on graphitic slips @ 40°. 70% recovery. (80.3 - 83.4) medium grey, minor green or tan streaks or bands. Bleached and slightly altered.	50595	73.0	74.0	1.0	0.002	0.02		
			50596	78.6	79.6	1.0	0.002	<0.02		
			50597	79.6	80.3	0.7	0.054	0.11		
			50598	80.3	81.3	1.0	0.002	0.02		
			50599	82.4	83.4	1.0	<0.001	<0.02		
83.4	84.7	QUARTZ VEIN (Main vein?) Grey and white with 10% altered foliated quartzite fragments, crackle breccia and fractures @ 10-30°. 1% pyrite, disseminated and along fractures, trace very fine grained disseminated galena. 90% recovery. Contacts sharp: upper contact irregular about 60°, lower contact @ 40°.	50600	83.4	84.1	0.7	0.002	0.03		
			50601	84.1	84.7	0.6	0.003	0.03		
84.7	101.2	CHLORITIC QUARTZITE (UNIT 2) Similar to (73.0 - 83.4). Upper 40cm tan to greenish grey. Foliation @ 75-80° (90.2 - 90.8) Bleached to medium green, grey and brown. Foliation @ 35-45°. (90.8 - 91.0) 20cm graphitic, crushed and broken core; slips @ 70-80°. (93.2 - 93.4) Broken, graphitic slips, 10cm graphitic and grey clayey gouge @ 70-80° (93.4 - 94.9) Grey altered quartzite, minor scattered graphitic slips. (95.5 - 98.5) Broken core in 1-5cm sections, scattered graphitic gouge to 2cm @ 70-80° and thin slips in upper half of section; lower half with chloritic slips and minor quartz veinlets.	50602	84.7	85.7	1.0	0.002	0.02		
101.2		END OF HOLE								0.002, 0.03 - 1.3

DIAMOND DRILL HOLE LOG

CLIENT OLIVER GOLD CORP.
PROPERTY FAIRVIEW

LOCATION <u>WINDER 2</u>	MOLE NO. <u>SC94 - 18</u>
SECTION <u>8410N</u>	AZIMUTH <u>222°</u>
LATITUDE <u>8936.04N</u>	DIP <u>-60°</u>
DEPARTURE <u>11285.12E</u>	LENGTH <u>142.0m</u>
ELEVATION <u>737.49m</u>	PURPOSE <u>Test HWY & MV</u>
CORE <u>NQ</u>	STARTED <u>Nov. 15, 1994</u>
LOGGED BY <u>F.R. Haseard</u>	COMPLETED <u>Nov. 15, 1994</u>

FOOTAGE			DIP TESTS		LATITUDE		DEPARTURE	
TEST	FROM	TO	TOTAL	DIP	CUM	CUM	CUM	CUM
1	73.2m			-55°				
2	137.8m			-55°				

METRES		DESCRIPTION	CORE SAMPLES							AVERAGES
FROM	TO		NUMBER	FROM (m)	TO (m)	WIDTH (m)	Au (OPT)	Ag (OPT)		
		STORAGE: Fairview Core Shack ; HEIGHT OF CASING ABO W GROUND: 0.2m								
0	3.0	CASING								
3.0	93.0	BIOTITIC & CHLORITIC QUARTZITE (UNIT 2)								
		Dark to medium grey, greenish grey, locally banded with dark green or brown @ 65-70°. Trace disseminated fine-grained pyrite, locally on small fractures and as aggregates to 3mm. Minor scattered chloritic fractures @ 10-30° and @ 60-80°.								
		(32.6 - 32.8) Grey quartz vein, banded with quartzite in upper 5cm. Sharp lower contact @ 55°. Trace pyrite. Minor late quartz veinlets and fractures @ 20-30° and 45-50°.								
		(36.8 - 53.1) More biotitic than chloritic, brownish colour bands and foliation planes, locally bleached to greyish tan near clayey fractures and quartz veinlets, as at 38.7 - 39.8m and 44.3 - 48.6m.								
		(54.9 - 65.6) as (36.8 - 53.1).								
		(64.5 - 65.5) Light grey to tan, silicified about 20cm grey quartz vein, trace pyrite, @ 70-80°. Minor quartz stringers @ 10-30°.								
		(72.5 - 73.8) Weakly silicified, quartz stringers @ 10-20°, scattered narrow irregular quartz veins to 1cm @ 45°, broken core.								
		(73.8 - 81.3) As (72.5 - 73.8), very minor broken core.								
		(89.7 - 89.9) Two 5-8cm creamy and pale green altered sections @ 45° and 70° around quartz-healed fractures.								
		(92.2 - 93.0) Dark greenish-black to black, chloritic and graphitic, 1% pyrite as elongate aggregates subparallel to foliation @ 70°. Upper 50cm dominately chloritic and weakly fractured; lower 30cm with graphitic fractures and 1-3% siliceous fragments in chloritic matrix. Lower contact broken.	50603	92.2	93.0	0.8	<0.001	0.04		
93.0	100.9	FAULT ZONE and HANGING WALL QUARTZ VEIN								
		(93.0 - 93.6) Light to medium grey, minor black bands, extremely crushed with bleached quartzite fragments to 5mm, minor graphitic bands, possibly some vein quartz material, trace pyrite. Contacts broken. 90% recovery.	50604	93.0	93.6	0.6	<0.001	<0.02		
		(93.6 - 95.4) Graphitic gouge, finely crushed grey quartzite or vein quartz. Core recovered in 5-8cm sections but considerable material ground or washed out. 40% recovery.	50605	93.6	95.4	1.8	0.003	0.03		

DIAMOND DRILL HOLE LOG

		FOOTAGE			DIP		LATITUDE		DEPARTURE	
TEST	FROM	TO	TOTAL		CORR.		CUM		CUM	
1	70.1m				-58°					
2	131.4m				-57°					

CLIENT OLIVER GOLD CORP.
PROPERTY FAIRVIEW

LOCATION WINDER 2
SECTION 8A40N
LATITUDE 8951.43N
DEPARTURE 11258.97E
ELEVATION 738.53m
CORE NO
LOGGED BY F.R. Hassard

HOLE NO. SC94 - 19
AZIMUTH 222°
DIP -63°
LENGTH 131.4m
PURPOSE Test HWV & MV
STARTED Nov. 17, 1994
COMPLETED Nov. 18, 1994

METRES		DESCRIPTION	CORE SAMPLES						AVERAGES
FROM	TO		NUMBER	FROM	TO	WIDTH	Au	Ag	
				(m)	(m)	(m)	(OPT)	(OPT)	
		STORAGE: Fairview Core Shack							
		HEIGHT OF CASING ABOVE GROUND: 0.3m							
0	3.0	CASING							
3.0	31.0	BIOTITIC QUARTZITE (UNIT 2) Medium grey and brown, finely foliated @ 60-70°. Minor scattered quartz stringers @ 10-40°. 5% biotite, 1-3% chlorite, trace disseminated fine-grained pyrite. (3.0 - 6.1) Limonite-stained fractures, broken core. (6.1 - 7.8) Dark greenish, minor 10-30cm irregular zones of yellowish-green alteration. (17.0 - 17.3) Quartz stringers and vuggy veinlets to 5cm @ 5-60°; slightly bleached to creamy pale brown. (19.5 - 20.0) Bleached to medium grey and tan layers about a central 3cm zone of clayey and graphitic gouge and slips @ 65-70°. Foliation @ 40°. (24.8 - 25.2) Bleached to sericitic quartzite near 5mm clayey gouge @ 45° at 25.1m.							
31.0	37.2	SERICITIC QUARTZITE (UNIT 3) Light to medium grey, streaked and banded by medium to dark grey @ 70°. Finely fractured and veined by quartz stringers @ 20-40°; minor clay on fractures. Contacts gradational over 20-40cm as brown biotite becomes progressively paler and is altered to sericite.							
37.2	81.5	CHLORITIC, BIOTITIC QUARTZITE (UNIT 2) As (3.0 - 31.0) with sections up to 3m more chloritic than biotitic. Foliation @ 65-70°. (44.3 - 45.0) three 5-10cm quartz veins, barren, contacts diffuse or sharp along foliation @ 65°. 50617 (55.1 - 56.2) Quartz Vein. White, minor greyish or brownish streaks. 15cm grey altered quartzite near upper contact. Trace disseminated pyrite, locally to 1% on fractures, trace chalcopyrite blebs to 1mm. Upper contact @ 65°; lower @ 30-40°. 95% recovery. 50618	50617	54.1	55.1	1.0	<0.001	<0.02	
			50618	55.1	56.2	1.1	<0.001	<0.02	

METRES		DESCRIPTION	CORE SAMPLES								
FROM	TO		NUMBER	FROM (m)	TO (m)	WIDTH (m)	Au (OPT)	Ag (OPT)	AVERAGES		
		(19.6) 5cm irregular fractures, pyrite, chloritic, bleached margins.									
		(20.55) 1-3mm pyritic quartz stringers @ 80°.									
		(26.4 - 29.9) Light grey, whitish, about vuggy quartz vein, broken core, 30cm ground core.									
		(29.0) 10cm quartz vein @ 35°, 5mm clay gouge at upper contact.									
		(30.3 - 30.8) Medium brown, light green, clay alteration & relict quartz bands @ 30°.									
		(30.8 - 32.9) Medium grey-brown, blotchy green, chloritic, massive, sparse 1-10mm quartz veins, irregular @ 10-30°.									
41.4	75.8	BIOTITIC QUARTZITE (UNIT 2) Dark grey to greyish brown, occasionally light grey, fine-grained, finely laminated, foliation @ 60-70°; moderately hard to very hard bands.									
		(43.7) 5cm quartz vein @ 60°, blebby quartz and 3-7% pyrite.									
		(51.7 - 55.3) 3-15mm quartz vein & bleached quartz stringers @ 15-25°, sparse 1-2 mm blebs of pyrite at vein margins and in host rock.									
		(60.0 - 75.8) Sericitic Quartzite (Unit 3)									
		(69.5 - 71.0) light grey, irregularly speckled with black, medium-grained, massive 90% quartz, 3% disseminated pyrite.	50636	74.8	75.8	1.0	< 0.001	< 0.02			
75.8	80.8	GRAPHITIC BRECCIA Dark grey, black, white; fragments < 1-5mm, occasionally to 10mm. 30% light grey to white quartz fragments in light grey to black quartz & graphite matrix, 3% disseminated pyrite; occasional 5-10cm sections light grey sericitic quartzite.	50637	75.8	76.8	1.0	0.004	0.04			
		(75.9) 20cm ground core	50638	76.8	77.8	1.0	0.004	0.04			
		(78.5 - 79.4) White vein quartz, 1% 1-2mm blebs pyrite, occasional 3mm vug.	50639	77.8	78.8	1.0	0.004	0.04			
		(80.2) 10cm ground core.	50640	78.8	79.4	0.6	0.002	0.04			
		(79.4 - 80.8) graphitic slicks @ 50°, sparse 3mm vugs lined with euhedral quartz. 2-5mm irregular bands fine-grained pyrite over 2cm at lower contact.	50641	79.4	80.2	0.8	0.003	< 0.02			
			50642	80.2	80.8	0.6	0.004	0.05			
80.8	92.4	QUARTZ VEIN ZONE (Hanging Wall Vein) (80.8 - 83.3) White vein quartz, fine-grained, massive; relict white subangular quartz fragments in light grey quartz matrix, 50% fragments; core broken 1/2-3cm pieces.. Sparsely mineralized - 1/2-1mm blebs galena & red brown sphalerite on wispy grey irregular fracture over 2cm at 81.7m. Ground core at: 81.7m, 30cm; 82.6m, 40cm; 83.2m, 5cm.	50643	80.8	81.7	0.9	0.004	0.07			
			50644	81.7	83.3	1.6	0.004	0.06			

METRES		DESCRIPTION	CORE SAMPLES										
FROM	TO		NUMBER	FROM	TO	WIDTH	Au	Ag	Au**			AVERAGES	
		(83.3 - 85.1) Chloritic quartzite. Dark green-grey, fine-grained, finely banded chlorite, quartz, graphitic in part; upper and lower contacts broken.	50645	83.3	84.5	1.2	<0.001	<0.02	(OPT)	** Screened for Metallics	↑	Au, Ag - Width (OPT) (m)	
			50646	84.5	85.1	0.6	0.004	0.04					
		(85.1 - 85.7) Quartz Vein. White medium-grained, massive; irregular rough fract. Sparse mineralization: 0.1-2mm blebs chalcopyrite, galena, 0.1mm red brown sphalerite; lower contact @ 60° along 3mm irregular band of fine-grained pyrite and graphite.	50647	85.1	85.7	0.6	0.102	0.71					
			50648	85.7	86.7	1.0	0.008	0.03					
		(85.7 - 88.2) Sericitic Quartzite. Medium grey, fine-grained, moderately-finely banded 1-5mm @ 50°. 1X disseminated pyrite 1-3mm blebs.	50649	86.7	87.7	1.0	0.065	0.04					
			50650	87.7	88.2	0.5	0.003	<0.02					
		(88.2 - 88.6) Quartz Vein. Banded white-grey and green, fine-to medium-grained, bands 3-7mm @ 65°; upper & lower contact sharp @ 45-55°. 3-7% pyrite, disseminated & irregular 1-3mm blebs in greyish bands with sericite & graphite; sparse 1mm blebs chalcopyrite 1/4%, minor galena; visible Native Gold as several fine specks along a 3mm plane with galena and other sulphides at 88.3m.	50651	88.2	88.6	0.4	0.004	0.03	0.353				0.051, 0.12 - 11.6
			50651Q	1/4 core split				0.93	0.915				
		(88.6 - 89.9) Sericitic Quartzite. Dark grey to medium greenish grey, fine-grained, irregularly finely banded 1-5mm @ 50°, occasional irregular 5-15mm quartz stringer. Trace sulphides.	50652	88.6	89.9	1.3	0.291	0.75	(assay suspect)				0.127, 0.20 - 3.4
			50652	reassay			0.002	<0.02					
			50652Q	1/4 core split			0.003	<0.02					
		(89.9 - 91.6) Quartz Vein. White, dark grey, brassy; medium-grained; coarsely banded to massive, bands @ 40°. Mineralization: 10% coarse 3-15mm blebs pyrite, 0.1-3mm disseminated pyrite, chalcopyrite, sphalerite blebs on irregular healed fracture, 0.1% dis. chalcopyrite. Massive white quartz vein with ghost breccia texture in part; 2-3mm white fragments in light grey quartz matrix. Lower contact sharp @ 50°.	50653	89.9	90.4	0.5	0.016	0.11	0.017				
			50654	90.4	90.9	0.5	0.095	0.36					
			50655	90.9	91.6	0.7	0.011	0.10					
		(90.4 - 90.9) 3-15mm blebs 1/2-1mm subhedral grains pyrite.											
		(91.6 - 92.1) Sericit Quartzite. Light grey, greenish grey; fine-grained, 3X 1-3mm blebs pyrite.	50656	91.6	92.1	0.5	0.002	0.02					
		(92.1 - 92.4) Quartz Vein. Black to light grey, graphitic, fine-grained, coarsely banded 3-7mm, slickensided @ 60°; 1-3mm blebs pyrite subparallel to banding in graphitic partings. Contacts sharp @ 60°.	50657	92.1	92.4	0.3	0.027	0.07					
92.4	101.3	SERICITIC QUARTZITE (UNIT 3) Light greenish grey to grey, fine-grained, finely to moderately banded 2-20mm @ 60-70°; Occasional irregular 3-7mm white quartz veinlets perpendicular foliation Core moderately broken 5-20cm lengths. Mineralization: 1-3% sparse blebs pyrite 2-5mm on irregular quartz coated fractures.	50658	92.4	93.4	1.0	<0.001	0.03					
101.3	107.5	CHLORITIC QUARTZITE (UNIT 2) Medium grey green, medium-grained, massive to finely banded locally @ 60-70°. Occasional very irregular whitish vuggy quartz veinlets and breccia 3-20mm. May be Mafic low in part(?) (106.9 - 107.5) Medium to dark grey sericitic, graphitic quartzite.	50659	106.5	107.5	1.0	<0.001	<0.02					

DIAMOND DRILL HOLE LOG

TEST	FOOTAGE			DIP		LATITUDE		DEPARTURE	
	FROM	TO	TOTAL	COMP.	CUM.	CUM.	CUM.		
1	84.7m			-53°					
2	128.9m			-53°					

CLIENT OLIVER GOLD CORP.
PROPERTY FAIRVIEW

LOCATION WINDER 2
SECTION 8500N
LATITUDE 8997.13N
DEPARTURE 11218.70E
ELEVATION 739.16m
CORE NO. _____
LOGGED BY R.J. Beckert

HOLE NO. SC94 - 21
AZIMUTH 222°
DIP -57°
LENGTH 128.9m
PURPOSE Test HWV & MV
STARTED Nov. 21, 1994
COMPLETED Nov. 22, 1994

METRES		DESCRIPTION	CORE SAMPLES							AVERAGES
FROM	TO		NUMBER	FROM (m)	TO (m)	WIDTH (m)	Au (OPT)	Ag (OPT)		
		STORAGE: Fairview core shack								
		HEIGHT OF CASING ABOVE GROUND: 0.2m								
0	3.0	CASING								
3.0	21.8	BIOTITIC, CHLORITIC QUARTZITE (UNIT 2)								
		Light grey to brownish-grey, occasionally dark grey; fine-grained, indistinctly finely laminated @ 60-70°, occasionally massive, quartz & sericite in 1-5mm bands alternating with biotite & chlorite, fissile; sparse disseminated pyrite 1-2mm grains especially on foliation planes; occasional blebs of white quartz 1/2-3cm subparallel to foliation.								
		(3.0 - 8.7) Limonitic chloritic quartzite. Ground core: 30cm at 4.9-5.5m, 20cm at 7.6-8.7m.								
		(12.6 - 13.6) graphitic slickensides @ 20-30°, 3cm chloritic gouge.								
		(21.4 - 21.8) Quartz vein, white, massive, 1% euhedral pyrite, lower contact @ 80°.	50662	21.4	21.8	0.4	<0.001	<0.02		
21.8	25.9	INTERMEDIATE DYKE								
		Medium blue-grey, fine-grained, massive andesite. Upper contact irregular with quartz stringers, lower contact sharp @ 50°.								
		(23.4) Irregular 3-5mm quartz stringers, green clay slickensides @ 35° over 10cm.								
25.9	56.4	BIOTITIC QUARTZITE (UNIT 2)								
		Medium brownish-grey to grey; fine-grained, moderately to weakly laminated 2-5mm, occasional massive blue-green-grey sections; 30% biotite, 10% chlorite, 60% quartz; weakly fissile; 3% 3-7mm quartz blebs subparallel foliation @ 70-80°, 1% disseminated pyrite, sparse irregular 1-3mm quartz stringers @ 10-30°.								
		(30.1 - 31.7) Irregular cream-grey quartz stringers @ 0-20°, vuggy, 3-5mm, 3mm blebs of pyrite								
		(37.8 - 39.6) Light grey chloritic sericitic quartzite; pyritic, graphitic slickensides @ 50°.								
		(40.8) 5cm chlorite & rock fragment gouge @ 40°.								
		(41.5 - 42.8) Fold nose - foliation subparallel to core.								

METRES		DESCRIPTION	CORE SAMPLES							AVERAGES	
FROM	TO		NUMBER	FROM (m)	TO (m)	WIDTH (m)	Au (OPT)	Ag (OPT)			Au, Ag - width (OPT) (m)
		(43.2) 3mm pyrite vein @ 35°, 10cm bleached margins.									
		(45.1 - 45.6) Blue-grey, fine-grained, massive, intermediate-mafic dyke?									
		(48.1 - 48.7) Dark brown-grey, fine-grained; massive; patchy light green chlorite irregular white clayey fractures @ 0-15°.									
		(52.5 - 55.0) Foliation change: 70° at 52.5m, 60° at 55.0m from a 85° near 44.0m									
		(54.9) 3-7mm irreg. white vuggy quartz stringer @ 40°.									
		(56.5) tight "S" fold over 10cm, broken core.									
56.4	78.0	CHLORITIC SERICITIC QUARTZITE (UNIT 3) Light and medium grey, minor grey-brown; fine-grained; finely to moderately foliated, moderately fissile; light grey siliceous bands alternating with dark grey sericite & lesser pyrite and graphite bands; hard to moderately hard; core broken 10-40cm subparallel to foliation; sparse white quartz stringers 2-5mm irregular @ 5-30°.									
		(56.4 - 60.0) medium grey laminated quartzite, very hard, 90% quartz.									
		(60.8 - 61.2) massive, med. grey, moderately soft sericitic.									
		(65.3) 15cm silicified, brecciated quartzite, light grey.									
		(65.7 - 67.2) Intermediate-mafic dyke; dark greenish-brown; fine-grained, massive contacts obscured by veinlets and alteration.									
		(66.4) Irregular quartz stringers 1/2-1cm @ 0-60°, irregular blebs pyrite 3mm.									
		(67.4 - 68.8) 7% disseminated pyrite blebs 4-7mm in medium-dark grey quartzite.									
		(70.9) 10cm vuggy quartz vein, 40% grey silicified wallrock fragments.									
		(70.6 - 78.0) grey, hard to very hard, sericitic, pyritic - 5% disseminated fine grains and 3mm blebs.	50663	77.0	78.0	1.0	<0.001	<0.02			
78.0	86.7	QUARTZ VEIN ZONE (Hanging Wall Vein and Wallrock) (78.0 - 81.3) Quartz Vein. White, irregular patches and laminae dark grey; massive, indistinctly coarsely brecciated - cemented with dark grey quartz 20%; 7% subhedral pyrite 0.1-0.5mm in grey quartz, 2% of vein.	50664	78.0	79.1	1.1	0.021	0.54			
			50665	79.1	80.8	1.7	0.004	0.09			
			50666	80.8	81.3	0.5	0.004	0.12			
		(81.3 - 83.5) Graphitic Quartzite & Fault Zone. Black to dark grey, fine-grained weakly finely laminated @ 65°; core broken 1/2-2cm; graphitic slips @ 40-60°. 1/4cm graphitic clay gouge @ 65° at 82.0m	50667	81.3	82.0	0.7	0.003	0.05			
			50668	82.0	82.9	0.9	0.005	0.03			
			50669	82.9	83.5	0.6	0.001	0.02			
		(83.5 - 84.8) Quartz Vein. White, 0.1-2mm irregular black partings; medium to coarse-grained; massive to weakly foliated @ 80°; core broken 1/2-10cm, 30cm ground core. 1% 2-3mm subhedral blebs pyrite, 1-3% fine-grained disseminated pyrite on graphitic partings; sparse <1/4% light brown sphalerite.	50670	83.5	84.2	0.7	0.042	0.14			
			50671	84.2	84.8	0.6	0.037	0.46			
											0.013, 0.18 - 6.8

METRES		DESCRIPTION	CORE SAMPLES						AVERAGES
FROM	TO		NUMBER	FROM	TO	WIDTH	Au	Ag	
86.7	98.5	(84.8 - 86.1) Sericitic Quartzite (Unit 3). Light greenish-grey to medium grey; moderately laminated @ 60° 1-5mm, fine-grained.	50672	84.8	85.5	0.7	0.002	0.05	
			50673	85.5	86.1	0.6	0.003	<0.02	
		(86.1 - 86.7) Quartz Vgn. White, lesser grey; medium-grained; massive; upper contact sharp @ 70°; 0.1 - 1mm subhedral pyrite, occasional blebs 3-5mm. Irregular black fractures at 86.6m.	50674	86.1	86.7	0.6	0.011	0.05	
		BIOTITIC CHLORITIC QUARTZITE (UNIT 2)	50675	86.7	87.8	1.1	0.002	<0.02	
		Medium to dark grey, grey-brown; fine-grained; weakly-moderately foliated @ 70°; hard; 2% disseminated pyrite along biotitic laminae; core broken 10-40cm subparallel to foliation. Lower contact gradational.							
		(87.8) 10cm quartz vein; 1-2mm black irregular graphitic bands at margin. 2% disseminated pyrite.	50676	87.8	87.9	0.1	0.023	0.38	
			50677	87.9	88.9	1.0	<0.001	0.02	
		(88.5 - 89.0) Black graphitic quartzite, 5% pyrite.							
		(89.8 - 90.3) Felsic Dyke. Medium grey, massive, medium hard; wispy 0.1mm black irregular stringers; contacts @ 20°.							
		(89.7) 10cm graphitic pyritic quartzite, 3-5mm irregular bands of pyrite.							
98.5	106.4	BIOTITIC QUARTZITE (UNIT 2)							
		Dark blue-grey to brown-grey, occasionally medium grey; fine-grained; weakly to moderately foliated, 3-10mm laminae; sparse quartz stringers subparallel foliation 3-10mm and wispy sparse 1/4-3mm quartz stringers @ 0-70°; moderately hard. Foliation; 70° at 96.9m, @ 65° at 101.0m, @ 80° at 105.2m. Core broken 10-40cm subparallel foliation.							
		(104.6) Graphitic slickensides @ 55°.							
106.4	110.9	(105.6 - 106.4) Graphitic slickensides @ 55-65°, 40% 5-10mm quartz laminae.							
		CHLORITIC QUARTZITE (UNIT 2)							
		Dark to light grey; fine-grained; finely laminated in part; 5% disseminated & 1/4-2mm subhedral pyrite, graphitic on foliation, contorted in part, core broken 1/2-10cm.	50678	106.4	107.0	0.6	0.002	0.08	
		(106.7 - 108.1) Broken core, graphitic fractures, 1/4-3cm zones.	50679	107.0	108.5	1.5	0.003	0.06	
		(108.5) 4cm quartz vein; 5% 1-3mm blebs and 1/2mm euhedral grains pyrite, graphitic slips; contacts @ 60°.	50680	108.5	108.6	0.1	0.010	0.21	
		(108.1 - 108.8) Irregular 2-10cm folds - fold nose.							
		(108.8 - 109.5) Felsic Dyke; light grey, 5% wispy medium grey irregular bands 0.1-2mm throughout. 3% pyrite, disseminated and 3mm stringers; moderately soft; occasional irregular white clay stringers. Upper contact @ 35°, lower @ 30°.	50681	108.6	109.5	0.9	0.001	0.04	

DIAMOND DRILL HOLE LOG

FOOTAGE				DIP		LATITUDE		DEPARTURE	
TEST	FROM	TO	TOTAL	COMP.	CUM	CUM	CUM	CUM	CUM
1	75.0m			-68°					
2	154.2m			-67°					

CLIENT OLIVER GOLD CORP.
PROPERTY FAIRVIEW

LOCATION JINDER 2
SECTION 8500N
LATITUDE 8997.13N
DEPARTURE 11218.70E
ELEVATION 739.16m
CORE NQ
LOGGED BY R.J. Beckett

HOLE NO. SC94 - 22
AZIMUTH 222°
DIP -72°
LENGTH 154.2m
PURPOSE Test HW & MV below SC94-21
STARTED Nov. 22, 1994
COMPLETED Nov. 24, 1994

METRES		DESCRIPTION	CORE SAMPLES							AVERAGES
FROM	TO		NUMBER	FROM	TO	WIDTH	Au	Ag		
		STORAGE: Fairview Core Shack; HEIGHT OF CASING ABOVE GROUND: 0.3m		(m)	(m)	(m)	(OPT)	(OPT)		
0	3.0	CASING								
3.0	33.7	CHLORITIC QUARTZITE (UNIT 2) Dark and medium grey banded; fine-grained; weakly to moderately foliated @50° quartz laminae 3-15mm; 30% chlorite, 70% quartz; occasional quartz veinlets to 3cm. (6.8 - 7.5) 30% irregular white quartz veinlets. (8.7 - 10.8) Light green mafic, broken core, irregular fractures coated with quartz. (10.8) 1.2m ground core (11.1) Pyrite stringers, 2-3mm @ 40°. (27.8) 40cm broken core; graphitic & chloritic fractures. (31.1 - 32.9) Mafic Dyke. Medium to dark brown, grey-blue; fine-grained, massive; mottled grey-green. Uppercontact parallel foliation @ 50°, lower contact broken. (33.2 - 33.7) Graphitic slips @ 50-60°.	50684	7.1	7.5	0.4	<0.001	<0.02		
33.7	56.4	CHLORITIC SERICITIC QUARTZITE (UNIT 3) Medium and light grey, grey-brown; fine-grained; weakly to moderately foliated 3-5mm; moderately fissile; quartz 70%, chlorite 15%, sericite 15%, pyrite dissem- inated and on fractures 1-2%, graphite 0-2% on fracture planes. Foliation: 50° at 33.9m, 60° at 39.1m, 50° at 46.4m. Lower contact gradational over about 2m. (36.2) 20cm broken core & graphitic gouge & quartzite. (36.8) 2-3cm quartz, pyrite vein @ 15°; 30% pyrite, contact on graphitic slips. (37.4) 30cm irregular 3-7mm quartz veinlets and breccia @ 40°. (48.5 - 53.1) Biotitic; medium greenish-brown. (50.1) 3cm crumbly quartz vein & chloritic, graphitic gouge @ 50°. (55.9) Irregular 2-3mm pyritic stringers & 5-10mm quartz stringers, clayey margins @ 20°.	50685	11.1	11.2	0.1	<0.001	<0.02		
56.4	84.6	CHLORITIC BIOTITIC QUARTZITE (UNIT 2) Dark grey to grey-brown to black; fine-grained; weakly banded 3-7mm, up 15mm;	50686	36.6	36.9	0.3	<0.001	<0.02		

METRES		DESCRIPTION	CORE SAMPLES							AVERAGES
FROM	TO		NUMBER	FROM	TO	WIDTH	Au	Ag		
				(m)	(m)	(m)	(OPT)	(OPT)		Au, Ag - width (OPT) (m)
		quartz 70%, biotite 20%, chlorite 10%, occasional sections 0.3 - 1m finely banded quartzite, 90% quartz; core broken 10-30cm subparallel foliation @ 55°; sparse wispy 1-3mm quartz stringers @ 20-40°.								
		(62.8) 3cm chloritic gouge & irregular quartz blebs @ 50°.								
		(64.8 - 66.0) coarsely mottled, quartz blebs 1-2cm, subrounded, 80%.								
		(72.2) 1cm graphitic chloritic gouge @ 53°; 10cm contorted foliation from lower contact.								
		(74.0) 1cm quartz vein & quartz breccia @ 60°.								
		(79.4) 15cm bleached, 1cm gouge & graphitic slips @ 50°.								
		(82.4 - 83.5) Dark grey-brown, mottled blue-grey; fine-grained, massive; Mafic Dyke or band; contacts subparallel foliation.								
84.6	97.0	SERICITIC CHLORITIC QUARTZITE (UNIT 2)								
		Light grey, grey-brown, medium brown; fine-grained; massive-mottled-moderate to finely banded 3-5mm; very to moderately hard; interbedded chlorite-biotite and chlorite-sericite quartzite; foliation: 55° at 88.7m, 60° at 93.3m; 2% disseminated pyrite.								
		(84.6 - 87.4) massive, weakly banded, 80% quartz, 3% pyrite.								
		(94.2) 10cm graphitic quartzite.								
		(94.7) 14cm felsite dyke, light grey, massive.								
		(96.0) 20cm banded graphitic quartzite, graphitic slips, foliation @ 80°.	50687	96.0	97.0	1.0	0.001	0.03		
97.0	97.5	GRAPHITIC QUARTZITE (FAULT ZONE)								
		Black, fine-grained, weakly laminated @ 80-90°; graphitic slips on foliation.								
97.5	102.4	QUARTZ VEIN (Hanging Wall Vein)								
		Mottled medium grey-dark grey-white; medium-grained; massive, indistinctly brecciated; black, wispy, discontinuous graphitic, pyritic stylolites; core broken 1/2-4cm; 1.9m ground core in section. 1/2% disseminated euhedral pyrite, 5% pyrite blebs 1-3mm on black irregular graphitic, chloritic "stylolite" surfaces.	50688	97.0	97.5	0.5	0.001	0.02		
		(97.5 - 98.9) broken core, 0.9m ground.	50689	97.5	98.8	1.3	0.001	0.03		
		(99.7 - 100.6) 0.6m ground core.	50690	98.8	99.7	0.9	0.001	0.02		
			50691	99.7	100.7	1.0	0.006	0.14		
		(100.7 - 101.0) pyritic, graphitic pelitic quartzite; 5% disseminated pyrite; foliation @ 75°.	50692	100.7	101.0	0.3	0.001	0.03		
		(101.0 - 102.4) very broken - gravel; 0.6m ground core.	50693	101.0	102.4	1.4	0.014	0.06		
		(102.3) 5cm 15% pyrite blebs 1-3mm, graphitic slips.								0.027, 0.06 - 4.9

METRES		DESCRIPTION	CORE SAMPLES									
FROM	TO		NUMBER	FROM	TO	WIDTH	Au	Ag	Au**	** Screened	for metallics	AVERAGES
			(m)	(m)	(m)	(OPT)	(OPT)	(OPT)			Au, Ag - width (OPT) (m)	
		(26.1 - 27.1) broken core, 30 cm ground core.										
		(27.7 - 29.2) 1.4m ground core.										
		(29.6 - 30.8) very irregular white to light grey quartz stringers and vuggy quartz breccia; 1-5mm pyrite blebs, irregular chloritic fractures.	50695	29.5	30.1	0.6	<0.001	<0.02				
			50696	30.1	30.8	0.7	0.004	0.02				
		(30.8 - 40.4) Light grey to grey-brown; fine-grained; wispy 0.1-1mm pyritic stringers @ 10°. 5cm clay gouge @ 75° at 32.1m.	50697	32.5	33.1	0.6	<0.001	<0.02				
		(32.8) 10cm light grey chloritic felsite; moderately soft.										
		(33.1) 10cm quartz vein; 3-7mm pyrite blebs; @ 70°.	50698	33.1	33.2	0.1	<0.001	<0.02				
33.4	47.4	CHLORITIC QUARTZITE (UNIT 2)	50699	33.2	33.8	0.6	<0.001	<0.02				
		Medium grey to grey-brown; fine-grained; weakly to moderately foliated @60-70°; 85% quartz, 10% chlorite; 3% sparse very fine grained disseminated biotite, 2% pyrite.										
		(36.8) 10cm 3-5mm quartz stringers and wallrock fragments.										
		(38.8 - 39.2) 1/2-2cm brown biotite-chlorite bands @ 65°; 1-2mm quartz stringers trace pyrite @ 0-40°.										
		(42.1 - 42.9) tight cm-scale fold noses - fold nose. 5mm clay gouge & 5mm quartz stringers @ 50° at 42.8m.										
		(43.6 - 47.4) broken core, 1.4m ground core.	50700	44.5	47.4	2.9	<0.001	<0.02				
47.4	51.9	QUARTZ VEIN (Hanging Wall Vein)										
		White, massive, coarse-grained, brecciated in part; pyritic & graphitic stylonites; ghost breccia texture, 70%, fragments 2-5mm; 3% pyrite, less than 1% galena and sphalerite, less than 1/2% chalcopryrite.										
		(47.4 - 48.3) Quartz vein breccia, 40% 1-5mm fragments of vein quartz and quartzite in cream quartz matrix.	66701	47.4	48.3	0.9	0.003	0.04				
		(47.6) pyritic - graphitic fractures and slickensides @ 30-50°.										
		(48.2) 10cm graphitic, clayey and rock fragment gouge @ 60°.										
		(48.3 - 48.8) Light grey quartz vein breccia, 1/2-3mm white fragments in grey matrix; 1-2cm banded medium to light grey quartz vein; 3% fine-grained disseminated pyrite and 5% 1-3mm blebs pyrite; 0.1-2mm blebs galena, about 1% 1mm blebs sphalerite and chalcopryrite; graphitic fractures or layers @ 40-60°.	66702	48.3	48.8	0.5	0.527	8.06	0.479			
		(48.8 - 49.4) diffuse 1/2-2cm patches light grey, fine-grained disseminated galena.	66703	48.8	49.4	0.6	0.032	0.29				
			66704	49.4	50.4	1.0	<0.001	0.02				
		(49.4 - 51.4) White, coarse-grained massive quartz vein; sparse grey fractures, fine-grained galena.	66705	50.4	51.4	1.0	<0.001	<0.02				
											0.064, 1.04 - 4.5	

DIAMOND DRILL HOLE LOG

FOOTAGE			DIP TESTS		LATITUDE	DEPARTURE
TEST	FROM	TO	TOTAL	CORR.	CUM	CUM
1	116.7m			-60°		

CLIENT OLIVER GOLD CORP.
PROPERTY FAIRVIEW

LOCATION WINDER 2
SECTION 8530N
LATITUDE 9013.58N
DEPARTURE 11192.84E
ELEVATION 742.36m
CORE NQ
LOGGED BY R.J. Beckett

HOLE NO. SC94-24
AZIMUTH 222°
DIP =62°
LENGTH 120.7m
PURPOSE Test HW & MV below 94-23
STARTED Nov. 26, 1994
COMPLETED Nov. 28, 1994

METRES		DESCRIPTION	CORE SAMPLES							
FROM	TO		NUMBER	FROM (m)	TO (m)	WIDTH (m)	Au (OPT)	Ag (OPT)	AVERAGES	
		STORAGE: Fairview Core Shack HEIGHT OF CASING ABOVE GROUND: 0.4m								
0	6.1	CASING								
6.1	24.5	CHLORITIC QUARTZITE (UNIT 2) Dark greenish grey, medium & light grey; fine- to medium-grained; well to moderately foliated @ 50-60°, 2-5mm occasionally 1-2cm; moderately to weakly fissile; 30% chlorit., 70% quartz; some sections 50cm-2m medium-light grey, 80% quartz 15% chlorite, 5% biotite. Lower contact sharp. (7.6 - 9.8) Linonitic fractures. (12.4 - 13.5) Light greenish grey, massive, coarse-grained; irregular 3mm white quartz stringers @ 0-30°; 5% disseminated pyrite; lower contact sharp @ 60°. (13.5 - 13.7) wispy graphitic fractures and slickensides @ 75°. (16.2) 2cm graphitic gouge @ 65°. (16.5) 20cm broken core, graphitic slips @ 55°. (19.4 - 20.2) 90% quartz, blue-grey quartzite; foliation @ 60°. (22.0 - 23.5) finely laminated quartzite, 90% quartz; irreg. 1/4-1cm quartz stringers @ 0-20°.	66717	12.4	13.5	1.1	<0.001	<0.02		
24.5	43.1	SERICITIC QUARTZITE (UNIT 3) Medium to light grey, fine-grained; finely foliated 1-5mm @ 75-90°; Quartz 70%, sericite 20%, chlorite 10%, 1-3% disseminated pyrite. Small scale fold noses, 5cm open at 27.1m & 38.9m. (24.5 - 25.8) Altered felsite (?); light grey, fine-grained, massive, moderately soft, sericitic; 2% disseminated pyrite. 5cm clay gouge @ 0-40°. (25.8 - 26.4) Breccia; 3-15mm quartzite fragments in white quartz matrix. (26.4 - 26.7) clay gouge @ 15°; clay-altered wallrock. (28.1 - 28.5) broken core, clayey fractures @ 40°. (29.3 - 29.6) broken core	66718	26.4	26.7	0.3	0.004	<0.02		

METRES		DESCRIPTION	CORE SAMPLES							AVERAGES	
FROM	TO		NUMBER	FROM (m)	TO (m)	WIDTH (m)	Au (OPT)	Ag (OPT)			Au, Ag - width (OPT) (m)
		(74.5 - 74.9) quartz vein breccia; irregular 3-5mm pyritic stringers.									
		(75.2 - 76.8) 3-5mm irreg. white quartz stringers; 1/3-3mm pyritic fractures @ 0°.									
		(81.0 - 81.9) crumbly quartz & graphite gouge; upper contact @ 45°, lower contact at graphitic slip & 1cm plastic gouge @ 50°.									
		(81.9 - 82.5) banded dark grey and black @ 40°, 5% disseminated pyrite.									
83.8	87.3	QUARTZ VEIN (Hanging Wall Vein)	66727	82.9	83.8	0.9	0.003	0.02			
		White, 1-3cm irregular bands & patches black; wispy black laminae @ 65°; medium-grained, massive to weakly banded; 5% pyrite, disseminated 1-2mm in patches on & adjacent to irregular, stylolitic graphitic fractures; 1/2% 1-2mm blebs light brown sphalerite, sparse galena on fractures.									
		(84.1) 1-3mm blebs sphalerite.	66728	83.8	84.1	0.3	0.010	0.03			
			66729	84.1	84.9	0.8	0.009	0.11			
		(84.9 - 85.3) 10% pyrite, disseminated & 1-3mm stringers.	66730	84.9	85.3	0.4	0.054	0.09			
			66731	85.3	85.6	0.3	0.059	0.05			
		(85.6 - 86.9) Sericitic quartzite; grey-brown to white, fine-grained, weakly banded with irreg. white quartz blebs subparallel to foliation; 80% quartz.	66732	85.6	86.4	0.8	0.005	<0.02			
			66733	86.4	86.9	0.5	0.003	<0.02			
		(86.9 - 87.3) white vein quartz, black graphitic stylolites; disseminated pyrite, sparse sphalerite & galena adjacent to stylolites.	66734	86.9	87.3	0.4	0.016	0.22			
87.3	100.2	BIOTITIC CHLORITIC QUARTZITE (UNIT 2)	66735	87.3	88.0	0.7	0.004	0.05			
		Medium to dark brown grey finely banded with medium grey 1-5mm @ 50-60°; moderately fissile, graphitic in part; 1-2mm disseminated pyrite esp. on foliation									
		(88.4 - 89.4) dark grey-black graphitic quartzite, 7% 1-5mm pyrites.									
		(95.8 - 96.8) quartz stringers subparallel core.									
		(97.7) 4cm quartz vein @ 55°, 10cm quartz blebs, 5% pyrite.									
100.2	109.3	CALCAREOUS MAFIC SCHIST									
		Dark greenish-grey to light green grey; fine- to medium-grained; finely laminated and banded; 3-10mm calcareous bands in mafic schist; 60% quartz, 10% biotite, 10% hornblende, 10% calcite; core broken 10-60cm.									
		(105.2 - 106.5) medium grey, siliceous; broken core, clayey fractures.									
		(107.6 - 109.3) light-medium green-grey mafic limestone.									
109.3	113.8	BIOTITIC MAFIC QUARTZITE (UNIT 2)									
		Black, dark grey-greenish grey; fine-grained; finely laminated @ 55-70°; 70% quartz, 20% mafics, 10% biotite, 2% disseminated pyrite									
		(111.9) 10cm graphitic gouge and crushed quartzite @ 50°.									

0.018, 0.07 - 3.5

METRES		DESCRIPTION	CORE SAMPLES						AVERAGES				
FROM	TO		NUMBER	FROM	TO	WIDTH	Au	Ag					
		(105.9 - 106.7) Graphitic quartzite.											
		(106.9 - 107.8) Crumbly graphitic gouge.	66747	105.9	106.7	0.8	0.009	0.09					
			66748	106.7	107.8	1.1	0.007	0.12					
			66749	107.8	108.8	1.0	<0.001	0.02					
		(109.9 - 111.4) Shattered quartzite & plastic graphitic gouge; graphitic slips @ 50-55°, occasionally @ 80-90°.	66750	108.8	109.9	1.1	0.001	0.02					
			66751	109.9	110.5	0.6	0.001	0.03					
			66752	110.5	111.2	0.7	0.001	0.02					
112.0	113.7	CHLORITIC SERICITIC QUARTZITE (UNIT 3)											
		Light greenish-grey, fine-grained, moderately laminated @ 50°; 70% quartz, 20% chlorite, 10% sericite; locally 10-20cm bands graphitic quartzite; 2% pyrite disseminated and 1-2mm stringers parallel foliation.	66753	113.2	113.7	0.5	0.001	0.03					
113.7	114.3	QUARTZ VEIN (Hanging Wall Vein Splay?)											
		White coarse-grained, massive quartz vein with black graphitic seams and stylolites; 3% pyrite, disseminated with graphite, 5-7mm stringers @ 50°, and irregular 1-2mm stringers; 1% disseminated galena. Upper contact sharp @ 55°, lower contact broken. 60% recovery.	66754	113.7	114.3	0.6	0.009	0.13					
114.3	115.2	SERICITIC QUARTZITE BRECCIA											
		Light grey, coarse-grained, 60% brecciated quartzite fragments 1mm-2cm, sub-angular, in light grey sericitic quartz matrix; graphitic slips @ 40°.	66755	114.3	115.2	0.9	<0.001	<0.02					
115.2	135.2	GRAPHITIC SERICITIC QUARTZITE (UNIT 3)											
		Light grey, dark grey, greenish grey; fine-grained; moderately laminated 1mm-2cm; includes sericitic, chloritic and graphitic quartzites and some well-laminated mafic tuff interbeds; foliation @ 45-55°; graphitic slips locally, parallel foliation; core broken 10-40cm, @ about 50°.	66756	115.2	115.5	0.3	0.004	0.06					
		(121.6 - 125.9) Light grey laminated quartzite.											
		(123.2) 3-7mm irregular pyritic stringers @ 30°.											
		(127.9 - 128.9) well laminated mafic tuff, grey green, chloritic.											
		(130.8) open 10-20cm fold in banded quartzite; crushed core & graphitic slips @ 30-60°; irregular quartz stringers.											
		(132.3 - 135.2) Chloritic, bleached, light green, laminated; discontinuous pyritic stringers.											
135.2	139.2	GRAPHITIC QUARTZITE BRECCIA and QUARTZ VEIN (Main Vein?)											
		Dark grey, black and white; graphitic breccia with quartz vein and quartzite fragments in graphite, quartz matrix; numerous irregular graphitic slips throughout; 80% quartz and quartzite fragments; core broken 3-10cm; 2% disseminated pyrite locally irregular white quartz stringers to 3mm. 0.3m ground core.	66757	135.2	136.2	1.0	0.007	0.13					
			66758	136.2	137.2	1.0	0.009	0.08					
		(137.5) 2cm graphitic, clayey crushed rock gouge @ 90°.	66759	137.2	138.2	1.0	0.004	0.08					
		(138.4) 14cm felsite dyke; light grey, fine-grained.	66760	138.2	138.7	0.5	<0.001	0.02					

DIAMOND DRILL HOLE LOG

FOOTAGE				DIP		LATITUDE		DEPARTURE	
TEST	FROM	TO	TOTAL		CORR.		CUM		CUM
None									

CLIENT OLIVER GOLD CORP.

PROPERTY FAIRVIEW

LOCATION SILVER CROWN
 SECTION 8500N
 LATITUDE 8924.97N
 DEPARTURE 11152.94E
 ELEVATION 754.08m
 CORE NQ
 LOGGED BY R.L. Beckett

HOLE NO. SC94 - 26
 AZIMUTH 222^o
 DIP -67
 LENGTH 30.5m
 PURPOSE Test MV above SC94-1
 STARTED Nov. 30, 1994
 COMPLETED Dec. 1, 1994

METRES		DESCRIPTION	CORE SAMPLES						AVERAGES
FROM	TO		NUMBER	FROM (m)	TO (m)	WIDTH (m)	Au (OPT)	Ag (OPT)	
		STORAGE: Fairview Core Shack							
		HEIGHT OF CASING ABOVE GROUND: 0.3m							
0	3.0	CASING							
3.0	21.3	BIOTITIC QUARTZITE (UNIT 2)							
		Medium grey, brown grey; medium-grained; irregularly laminated 2-10mm @ 50-70° 1% disseminated pyrite.							
		(3.0 - 5.8) broken core, limonite-coated fractures; 1.2m ground core.							
		(4.4 - 4.8) 35cm Quartz Vein; white to grey, grey stylolites and limonite-coated fractures; broken core 2-4cm, 0.9m ground core; 2% pyrite, 1-2mm grains, 1% chalcopyrite. This vein may be a splay off the <u>Hanging Wall Vein</u> .	66775	4.4	4.8	0.4	0.028	0.17	
		(5.8 - 7.1) 80% quartz bands.							
		(7.6) tight, contorted folds over 20cm; axial plane @ 70° to Core axis.							
		(17.2) cm-scale open folds over 30cm.							
		(18.5) cm-scale folds over 30cm.							
		(20.5 - 21.3) 3% disseminated and 1-2mm stringers pyrite.	66767	20.8	21.3	0.5	0.019	0.19	
21.3	24.0	QUARTZ VEIN (Main Vein)							
		70% white, massive quartz, 30% dark grey quartz and weakly banded, silicified quartzite; 7% pyrite, disseminated and 1-3mm euhedral grains and fine-grained aggregates, less than 1% disseminated galena and light brown sphalerite with dark greyish quartz; sparse pyrite and galena with white quartz.							
		(21.3 - 22.0) irregular white to light grey quartz veins and sericitic, silicified and bleached wallrock.	66768	21.3	22.0	0.7	0.043	1.03	
		(22.0 - 22.1) 10cm band sericitic wallrock, 10% pyrite.	66769	22.0	22.5	0.5	0.024	0.31	
		(22.1 - 22.2) 12cm band dark grey to light grey quartz, 1-3mm irregular seams pyrite, 0.1-1mm blebs light brown sphalerite and galena.							
		(22.7) 10cm band 20% pyrite, disseminated and 1-5mm subhedral blebs.	66770	22.5	23.0	0.5	0.078	0.82	
			66771	23.0	23.5	0.5	0.017	0.52	
		(23.7 - 24.0) grey stylolites @ 50°; 3% pyrite, disseminated and 0.1-2mm grains, sparse 0.1-1mm blebs sphalerite and galena.	66772	23.5	24.0	0.5	0.103	0.89	
									0.052, 0.74-2.7

METRES		DESCRIPTION	CORE SAMPLES						AVERAGES
FROM	TO		NUMBER	FROM (m)	TO (m)	WIDTH (m)	Au (OPT)	Ag (OPT)	
24.0	30.5	BIOTITIC CHLORITIC QUARTZITE (UNIT 2) Dark grey, medium greenish grey; medium grained; finely to indistinctly laminated @ 60-80°; quartz 70%, biotite 20%, chlorite 10%. (24.1) 6cm white-grey quartz vein. (24.3) 10cm dark grey plastic clay gouge @ 75°. (24.4) 6cm quartz vein; less than 1% very fine grained pyrite and galena. (26.0) 40cm light greenish grey intermediate dyke, fine-grained, massive.							
			66773	24.0	24.6	0.6	0.004	0.81	
			66774	24.6	25.1	0.5	<0.001	0.04	
30.5		END OF HOLE							

METRES		DESCRIPTION	CORE SAMPLES									
FROM	TO		NUMBER	FROM	TO	WIDTH	Au	Ag	Au**	** Screened for meta	lics	AVERAGES
		Upper and lower contacts @ 80°.		(m)	(m)	(m)	(OPT)	(OPT)	(OPT)			
		(39.2 - 39.7) graphitic laminated quartzite; brown-black, fine-grained.	66779	38.7	39.2	0.5	0.516	6.60	0.475			Au, Ag - width
		(39.7 - 40.5) irregularly banded grey and white quartz vein; 5% pyrite, 1-3mm subhedral grains, 1/2% chalcopyrite and sphalerite.	66780	39.2	39.7	0.5	0.013	0.05				(OPT) (m)
40.5	52.0	BIOTITIC SERICITIC QUARTZITE (UNIT 3)	66781	39.7	40.5	0.8	0.090	0.32				0.176, 1.99 -1.8m
		Grey-green, medium grey; fine-grained; finely laminated to moderately banded; grey-brown biotitic sericitic quartzite and chert interbedded with grey-green mafic tuff.	66782	40.5	41.0	0.5	0.002	0.02				
		(43.6 - 45.3) Intermediate dyke; medium grey-green; fine-grained; massive; lower contact @ 30°.										
		(48.9 - 51.4) Intermediate tuff, well banded, calcareous; 1/2-1cm bands.	66784	51.5	52.0	0.5	0.010	0.11				
52.0	53.5	QUARTZ VEIN	66785	52.0	52.5	0.5	0.092	0.47				
		White, light grey, green; coarse-grained; massive; locally 1-10cm fragments of wallrock, sericitic and with 7% pyrite; vein quartz has 3% 1-5mm pyrite blebs, less than 1% chalcopyrite, galena and sphalerite.	66786	52.5	53.1	0.6	0.022	0.05				0.057, 0.20 -1.5m
		(53.1 - 53.5) 7% pyrite in wallrock fragments, trace chalcopyrite, galena, sphal.	66787	53.1	53.5	0.4	0.065	0.09				
53.5	57.0	CHLORITIC SERICITIC QUARTZITE (UNIT 3)										
		Grey, grey-brown; fine-grained; finely laminated, banded 2-10mm; finely laminated chert locally; foliation @ 70-80°.										
		(53.6 - 55.5) contorted lamination, irregular tight folds	66788	53.5	54.0	0.5	<0.001	< 0.02				
		(55.5 - 56.1) broken core.										
57.0	65.7	CALCAREOUS CHLORITIC MAFIC TUFF										
		Greenish grey, light green, light grey; fine-grained; finely laminated, banded 1-15mm; 7% 3-25mm layers light grey limestone; foliation @ 50-60°.										
		(65.2) 2cm white quartz vein.										
65.7	72.0	CHLORITIC QUARTZITE (UNIT 2)										
		Dark grey, medium grey; fine- to very fine grained; finely laminated, weakly banded; locally chert as 2-5mm laminae; 70% quartz, 20% chlorite, minor pyrite, disseminated and irregular 2-3mm blebs; foliation @ 40-60°.	66794	69.4	69.8	0.4	0.004	0.06				
		(65.8 - 67.0) very irregular folds, laminae subparallel to core. Fold nose.	66795	69.8	70.2	0.4	0.014	0.13				
		(66.7 - 67.0) 20% pyrite, irreg. 3-5mm blebs.	66796	70.2	70.6	0.4	0.023	0.21				
			66797	70.6	70.9	0.3	0.052	0.94				
			66798	70.9	71.5	0.6	0.008	0.10				
		(69.8 - 72.0) Bleached, 5% pyrite, disseminated and 1-3mm blebs.	66789	71.5	72.0	0.5	0.013	0.12				

METRES		DESCRIPTION	CORE SAMPLES								AVERAGES	
FROM	TO		NUMBER	FROM	TO	WIDTH	Au	Ag				
			(m)	(m)	(m)	(OPT)	(OPT)					Au, Ag - width (OPT) (m)
		(58.0 - 59.0) Mafic dyke; dark green, fine-grained, massive; light green blotches, irregular 1/2mm pyritic stringers; contacts parallel foliation.										
		(63.7 - 64.5) Mafic dyke; as (58.0 - 59.0).										
		(64.5 - 69.3) weakly laminated to massive quartzite; wispy 1/2-1mm pyrite stringers; local tight folds - fold nose.										
69.3	90.1	GRAPHITIC SERICITIC QUARTZITE (UNIT 3)										
		Dark grey, medium grey, light grey; weakly to finely laminated; 5-10% sericite locally 2% graphite and pyrite, disseminated and as partings; 1-2m beds medium grey-green; foliation @ 55-65°; sparse 1-2mm irregular quartz stringers @ 20-60°.										
		(70.2 - 72.1) grey-brown chloritic, pyritic quartzite; foliation @ 60°.										
		(73.2 - 75.8) 40% 10-30cm graphitic quartzite bands.										
		(78.6 - 82.2) light grey to white, massive quartzite; 1-10mm brecciated quartz veinlets.	66799	78.6	79.6	1.0	<0.001	<0.02				
			66800	79.6	80.4	0.8	0.001	<0.02				
			66801	86.7	87.2	0.5	<0.001	<0.02				
			66802	87.2	87.5	0.3	0.009	0.09				
		(87.2 - 90.1) broken core 1-5cm; 1.9m ground core; 10cm graphitic quartz vein. lower contact @ 45°, 3% disseminated pyrite, graphitic stringers.	66803	87.5	89.9	2.4	0.005	0.05				
			66804	89.9	90.3	0.4	0.004	0.11				
90.1	96.6	SERICITIC QUARTZITE (UNIT 3)										
		Light grey, medium grey; fine- to medium-grained; 90% quartz, 10% sericite, 1-2% pyrite, disseminated; foliation @ 65-70°; core broken parallel foliation 2-30cm.										
		(90.4) 2-5mm blebs & irreg. stringers pyrite over 10cm.	66805	90.3	90.8	0.5	0.001	0.03				
		(92.8 - 93.6) white, light grey breccia, fragments of quartzite 3-5mm, 70% in quartz cement; 2% pyrite, disseminated & 3-5mm blebs.										
		(93.6 - 93.9) 30cm dark grey graphitic quartzite.										
		(94.2 - 95.4) light grey-brown, dark grey; very fine grained, moderately to finely laminated quartzite.										
		(95.4 - 95.7) 30cm broken core.	66806	96.1	96.6	0.5	<0.001	<0.02				
96.6	97.2	QUARTZ VEIN (Main Vein)										
		White, light grey; medium-grained; wispy pyrite and irregular graphitic stylolites & irregular fractures; 5% pyrite as 2-5mm blebs & disseminated adjacent to stylolites; very broken, 1m ground core; local white-cream quartz stringers and cement to thin brecciated zones.	66807	96.6	96.8	0.2	0.012	0.47				
			66808	96.8	97.2	0.4	0.001	0.02				0.005, 0.17 -0.6m
97.2	99.4	GRAPHITIC QUARTZITE										
		Dark grey, black; very broken core, 1m ground core.	66809	97.2	99.4	2.2	<0.001	<0.02				

METRES		DESCRIPTION	CORE SAMPLES							AVERAGES	
FROM	TO		NUMBER	FROM	TO	WIDTH	Au	Ag	Au	Ag - width	
			(m)	(m)	(m)	(OPT)	(OPT)			(m)	
43.8	50.2	<p>GRAPHITIC SERICITIC QUARTZITE (UNIT 3)</p> <p>Dark grey, medium grey; fine-grained; irreg. weakly to moderately laminated, 85% quartz, 10% sericite, 3% graphite, 2% pyrite; core broken 3-20cm; foliation: @65° at 43.8, @ 60° at 48.5m.</p> <p>(43.8 - 44.5) broken core, graphitic fractures; irreg. 2-5mm quartz stringers @ 0-20°; brecciated with white quartz cement.</p> <p>(45.5 - 46.3) foliation @ 0°, open cm-scale folds.</p> <p>(46.3 - 48.8) grey-brown to green, fine-grained, massive mafic.</p> <p>(49.0 - 50.2) medium grey, sericitic, 3% 1-2mm pyritic stringers.</p>	66810	49.7	50.2	0.5	0.002	0.05			
50.2	62.5	<p>QUARTZ VEIN (Hanging Wall Vein) and SHEAR ZONE, SERICITIC QUARTZITE (UNIT 3)</p> <p>White, medium grey, medium- to fine-grained, massive quartz vein with dark to medium grey patches & wispy black stylolites; light grey sericitic quartzite, locally light green-grey containing fuchsite. Core very broken, 1/2-10cm; 20-30% recovery overall.</p> <p>(50.2 - 50.7) White quartz vein, sparse graphitic stylolites, 1% pyrite, 1/2% galena; 50% recovery.</p> <p>(50.7 - 53.6) Sericitic quartz fragments, 20% recovery.</p> <p>(53.6 - 56.7) Brecciated sericitic quartzite; 10% very irregular quartz stringers and quartz matrix; 3% disseminated pyrite.</p> <p>(56.7 - 57.1) Pyritic, sericitic quartzite; 7% disseminated pyrite, 7% light apple green fuchsite.</p> <p>(57.1 - 58.9) Quartz vein, white to light grey; 20% 1-3mm white quartz stringers cutting light grey quartz vein, locally vuggy; 40% recovery; lower contact @ 40°.</p> <p>(58.9 - 61.0) Sericitic quartzite.</p> <p>(61.0 - 61.5) Sericitic quartzite, 7% pyrite, disseminated & coating irregular foliation planes.</p> <p>(61.5 - 62.5) Quartz vein; white, medium grey, medium-grained, massive with wispy graphitic & pyritic stylolites, very irreg. late quartz stringers 1/2-2mm; upper contact @ 60°.</p> <p>(61.5 - 62.0) 5% disseminated pyrite, 0.1-1mm subhedral grains, 1% brown sphalerite 0.1mm stringers, 1% galena 0.1-1mm aggregates & irregular stringers.</p> <p>(62.0 - 62.5) 10% blue-grey quartz with indistinct outlines, 1% disseminated pyrite, 1/2% disseminated galena, graphitic stylolites over lower 10cm.</p>	66811	50.2	50.7	0.5	<0.001	<0.02			
			66812	50.7	53.6	2.9	<0.001	0.02			
			66813	53.6	56.7	3.1	0.003	0.06			
			66814	56.7	57.1	0.4	0.009	0.27			
			66815	57.1	58.9	1.8	<0.001	0.03			
			66816	58.9	59.4	0.5	0.002	0.04			
			66817	59.4	60.4	1.0	<0.001	<0.02			
			66818	60.4	61.0	0.6	<0.001	<0.02			
			66819	61.0	61.5	0.5	0.008	0.08			
			66820	61.5	62.0	0.5	0.043	0.28			
			66821	62.0	62.5	0.5	0.009	0.08			0.026, 0.18 -1.0m

METRES		DESCRIPTION	CORE SAMPLES							AVERAGES	
FROM	TO		NUMBER	FROM (m)	TO (m)	WIDTH (m)	Au (OPT)	Ag (OPT)	Au, Ag - width (OPT)	(m)	
62.5	68.9	<p>CHLORITIC BIOTITIC QUARTZITE (UNIT 2)</p> <p>Light grey-brown; fine-grained, weakly to moderately foliated @ 60°; 90% quartz, 5% chlorite, 5% biotite, 1-2% pyrite, disseminated & on fractures; core broken 5-40cm.</p>	66822	62.5	63.0	0.5	<0.001	<0.02			
68.9	76.0	<p>CALCAREOUS SILICEOUS MAFIC TUFF</p> <p>Medium to dark grey-green; fine-grained; finely laminated and banded 2-30cm; weakly calcareous; 20% 3-20mm light green quartz-rich bands & lamellae; weakly fissile; 80% mafics, 20% quartz, 1-5% calcite; foliation @ 60°.</p> <p>(71.0) 2cm quartz vein @ 60°.</p> <p>(71.2) 1cm black chloritic gouge @ 60°.</p> <p>(71.9) 4cm quartz-wallrock breccia, 40cm broken core.</p>									
76.0	79.3	<p>CHLORITIC BIOTITIC QUARTZITE (UNIT 2)</p> <p>Medium grey, moderately foliated @ 60-75°, medium-grained; 60% quartz, 30% biotite, 10% chlorite; moderately fissile.</p> <p>(77.2) chloritic gouge and crushed rock @ 80° over 10cm</p> <p>(78.0) 10cm grey quartz vein, 1/2-2mm graphitic lamellae spaced 3-10mm.</p> <p>(78.1 - 78.5) Intermediate dyke; light greenish grey, fine-grained, massive.</p> <p>(78.7 - 79.3) 5cm graphitic gouge, 3-5mm quartz stringers, broken core, 20cm ground core.</p>	66823	77.5	78.0	0.5	<0.001	0.02			
			66824	78.0	78.1	0.1	0.006	0.08			
			66825	78.1	78.7	0.6	<0.001	<0.02			
			66826	78.7	79.3	0.6	<0.001	<0.02			
79.3	81.4	<p>QUARTZ VEIN (Main Vein)</p> <p>White, light grey, black; medium-grained; massive to weakly banded; stylolites subparallel to contact @ 60°, graphitic; 2% pyrite, disseminated adjacent to stylolites & sparse 1-3mm blebs, 1% medium brown sphalerite, 1-2mm disseminated blebs adjacent to stylolites & occasionally in quartz matrix, 1% galena, fine-grained disseminated wispy patches & 0.1-0.5mm blebs.</p> <p>(79.9) 10cm light grey siliceous quartzite.</p> <p>(80.0) 30% dark grey to black pyritic & graphitic stylolites, 5% disseminated subhedral pyrite.</p> <p>(80.2) 6cm medium grey quartz, graphitic stylolites, numerous vuggy, and pyritic & graphitic fractures.</p> <p>(80.3 - 80.6) white quartz, sparse graphitic stylolites; 2-3mm blebs medium brown sphalerite, 2% patchy disseminated galena, 1/2-1mm grains, trace 0.1mm disseminated chalcopyrite grains.</p> <p>(80.6 - 81.1) white and black irregularly banded quartz vein; quartz stringers and pyritic, graphitic wallrock; 5% pyrite, disseminated & 2-5mm blebs; foliation @ 80°.</p>	66827	79.3	79.9	0.6	0.055	0.43			
			66828	79.9	80.3	0.4	0.058	1.08			
			66829	80.3	80.6	0.3	0.034	0.65			
			66830	80.6	81.1	0.5	0.007	0.04			
			66831	81.1	81.4	0.3	0.002	0.07			
										0.034, 0.44 -2.1m	

DIAMOND DRILL HOLE LOG

FOOTAGE			DIP TESTS		LATITUDE		DEPARTURE	
TEST	FROM	TO	TOTAL	DIP CORR.	CUM	CUM	CUM	CUM
1	45.5m			-49°				

CLIENT OLIVER GOLD CORP.
 PROPERTY FAIRVIEW

LOCATION SILVER CROWN HOLE NO. SC94 - 30
 SECTION 8450N AZIMUTH 222°
 LATITUDE 8886.92N DIP -53°
 DEPARTURE 11200.60E LENGTH 45.7m
 ELEVATION 740.61m PURPOSE Test HWV & MV above 94-14
 CORE NQ STARTED Dec. 5, 1994
 LOGGED BY R.J. Beckett COMPLETED Dec. 6, 1994

METRES		DESCRIPTION	CORE SAMPLES						AVERAGES	
FROM	TO		NUMBER	FROM (m)	TO (m)	WIDTH (m)	Au (OPT)	Ag (OPT)	Au, Ag - width (OPT) (m)	
		STORAGE: Fairview Core Shack								
		HEIGHT OF CASING ABOVE GROUND: 0.3m								
0	3.7	CASING								
3.7	11.3	BIOTITIC SERICITIC QUARTZITE (UNIT 3)								
		Medium grey, medium-grained; finely laminated, foliation @ 70-80°; quartz 60%, 30% sericite, 10% biotite; core broken 2-30cm.								
		(3.7 - 6.0) limonitic fractures and lost core.								
11.3	13.3	QUARTZ VEIN (Hanging Wall Vein)								
		White, patchy medium to dark grey, medium-grained; massive quartz with 1-5cm pyritic and graphitic patches; 2% pyrite, 1/2-2mm subhedral grains & 1-5mm blebs; upper contact sharp @ 85°.	66835	10.8	11.3	0.5	0.005	0.09		
		(11.3 - 11.7) 30% medium to dark grey quartz, 7% pyrite stringers 1-3mm.	66836	11.3	11.7	0.4	0.074	0.54		
		(11.7 - 12.8) massive white quartz, sparse black stylolites.	66837	11.7	12.2	0.5	0.012	0.02		
		(12.8 - 13.3) 20% pyritic dark grey patches, sparse 1/2mm blebs sphalerite, less than 1/2%.	66838	12.2	12.8	0.6	0.007	0.03		
			66839	12.8	13.3	0.5	0.010	0.03		
13.3	23.0	CHLORITIC BIOTITIC QUARTZITE (UNIT 2)								
		Medium to dark grey, fine-grained, moderately laminated 2-5mm; 70% quartz, 20% biotite, 10% chlorite, 1% disseminated pyrite; foliation @ 60-75°; contacts gradational.	66840	13.3	13.8	0.5	0.001	<0.02		
23.0	29.0	SERICITIC QUARTZITE (CHERT) (UNIT 3)								
		Medium to light grey, fine-grained; fine laminations 1-7mm, locally massive; numerous tight 3-10mm folds & cm-scale open folds; minor pyrite, disseminated & sparse 2-3mm blebs and irreg. stringers; minor 3-20mm irreg. white quartz stringers.								
		(23.0 - 23.7) massive, medium-grained, hard.								
		(24.4 - 27.0) tight folds.								
		(27.5 - 28.7) light grey, bleached, 7% disseminated pyrite, 2.5cm quartz veinlet @ 60°, white to light grey quartz with irreg. graphitic stylolites and 5% pyrite, clayey gouge at contacts. 20cm ground core.	66841	27.5	28.7	1.2	0.021	1.58		

0.022, 0.13 -2.0m

DIAMOND DRILL HOLE LOG

FOOTAGE				DIP		LATITUDE		DEPARTURE	
TEST	FROM	TO	TOTAL	CONG.		CUM		CUM	
1	45.7m			-61°					
2	86.6m			-60°					

CLIENT OLIVER GOLD CORP.
PROPERTY FAIRVIEW

LOCATION WINDER 2
SECTION 8440N
LATITUDE 8922.59N
DEPARTURE 11232.60E
ELEVATION 744.19m
CORE NO. NO
LOGGED BY R.J. Beckett

HOLE NO. SC94 - 31
AZIMUTH 222°
DIP -62°
LENGTH 87.0m
PURPOSE Test HWV & MV between 94-13 & 94-14
STARTED Dec. 6, 1994
COMPLETED Dec. 7, 1994

METRES		DESCRIPTION	CORE SAMPLES						AVERAGES
FROM	TO		NUMBER	FROM (m)	TO (m)	WIDTH (m)	Au (OPT)	Ag (OPT)	
		STORAGE: Fairview Core Shack							
		HEIGHT OF CASING ABOVE GROUND: 0.3m							
0	3.0	CASING							
3.0	46.1	SERICITIC QUARTZITE (UNIT 3)							
		Medium grey, grey-brown; fine- to very fine grained; finely to moderately laminated 2-5mm, foliation @ 75-85°; locally biotite laminae, locally chert; occasional 1-3mm quartz stringers @ 0°, 5-20cm bands dark grey to black, graphitic; 1% pyrite; occasional tight cm-scale folds.							
		(3.0 - 7.9) limonitic fractures & foliation planes.							
		(11.0 - 11.7) broken core, scattered clayey fractures.							
		(12.7 - 13.9) broken core.							
		(19.8 - 26.5) very siliceous, 1-5cm white quartz blebs, wispy 1-5mm bands dark green chlorite-actinolite, 2% disseminated pyrite.							
		(26.6 - 27.6) dark grey, green and buff, fine-grained, massive, mafic; locally bleached; 10cm cherty breccia with white quartz matrix and 5cm sandy clay gouge @ 30° at end of section.							
		(30.1 - 31.1) broken core.							
		(36.5 - 40.3) dark grey, fine-grained, finely laminated, very hard.							
		(38.8 - 40.3) open folds, 1-10cm.							
		(41.4 - 46.1) very broken core, 1/2-7cm, very siliceous.							
46.1	48.7	FAULT ZONE (Breccia, Gouge, Quartz Veins)							
		(46.9 - 47.0) 10cm black crumbly graphitic gouge, contact sharp @ 50°.	66848	46.1	46.5	0.4	0.001	<0.02	
		(47.0 - 47.3) Quartz vein; white, medium grey, medium-grained, 1% pyrite disseminated throughout, upper contact sharp @ 50° along graphitic slip, lower contact brecciated with white vuggy quartz matrix, numerous quartz veinlets.	66849	46.5	47.0	0.5	<0.001	<0.02	
		(47.3 - 48.0) light grey sericitic quartzite, cut by irreg. quartz stringers 1-3mm.	66850	47.0	47.3	0.3	0.163	0.08	
			66851	47.3	48.0	0.7	0.004	<0.02	

METRES		DESCRIPTION	CORE SAMPLES									
FROM	TO		NUMBER	FROM	TO	WIDTH	Au	Ag	Au**	**Screened fo	metallics	AVERAGES
			(m)	(m)	(m)	(OPT)	(OPT)	(OPT)			Au, Ag - width (OPT) (m)	
48.7	52.7	(48.0 - 48.7) Breccia; 70% 1-30mm subangular quartz & sericitic quartzite fragments in gougy chloritic & minor graphitic matrix. BIOTITIC SERICITIC QUARTZITE (UNIT 3) Medium brownish grey, fine-grained, finely laminated, foliation @ 55°; 70% quartz, 15% sericite, 15% biotite; local 3-10cm bands black graphitic quartzite; 3% disseminated pyrite in graphitic bands, generally 1% pyrite; lower contact gradational over 3cm.	66852	48.0	48.7	0.7	0.021	0.04				
52.7	54.4	QUARTZ VEIN (Hanging Wall Vein) White with 3-20 mm patches dark to medium grey quartz; medium-grained; very irreg. wispy patches grey sulphides; irreg chloritic fractures @ 60°; wispy 1-3mm chlorite & graphite partings & lamellae; 2% 0.1-2mm disseminated pyrite, 1% 0.1-1mm light brown sphalerite, 1/2% disseminated galena, trace disseminated chalcopyrite. Lower contact broken.	66853	52.3	52.7	0.4	<0.001	<0.02				
54.4	69.2	(53.2 - 53.9) 40% black chlorite-graphite shreds - higher than general pyrite & sphalerite content, local graphitic slips. (53.9 - 54.4) white quartz, 5% wispy black-yellow blebs 2-7mm; pyrite, sphalerite, galena & chalcopyrite.	66854	52.7	53.2	0.5	0.150	1.59				
		(53.2 - 53.9) 40% black chlorite-graphite shreds - higher than general pyrite & sphalerite content, local graphitic slips.	66855	53.2	53.9	0.7	0.515	1.59	0.474		0.298, 1.85 -1.7m	
54.4	69.2	SERICITIC BIOTITIC QUARTZITE (UNIT 2) Medium brownish grey, fine-grained, well to moderately laminated 1/2-5mm, foliation @ 55-65°, irreg. quartz lamellae 2-5mm with sericitic, biotitic lamellae 1/2-2mm; occasional grey quartz blebs 1/2-5cm subparallel to and cross-cutting foliation; 1% disseminated pyrite and sparse 1-3mm quartz stringers.	66856	53.9	54.4	0.5	0.199	2.46				
69.2	80.3	(56.3 - 57.3) contorted quartz lamellae. (61.9) 15cm quartz stringer subparallel to foliation. (61.1 - 62.8) broken core, chloritic fractures parallel foliation. (62.8 - 66.7) dark grey, chloritic. (67.0 - 68.1) medium grey, sericitic quartzite.	66857	54.4	54.9	0.5	0.003	0.03				
69.2	80.3	CALCAREOUS SILICEOUS MAFIC TUFF Dark grey-green; light green; fine-grained; finely banded, laminated; 3-15mm light green calcareous bands, 80% calcite; irreg. 1/2-3mm quartz stringers @ 5-30°; foliation @ 55-65°. (78.8 - 80.3) 10% irreg. quartz blebs 1-5mm; distorted fine lamellae, siliceous, 1% calcite, graphitic foliation planes. (79.1 - 80.3) irreg. graphitic slips & 1-3mm quartz stringers.	66858	79.7	80.3	0.6	0.002	<0.02				

DIAMOND DRILL HOLE LOG

FOOTAGE				DIP		LATITUDE		DEPARTURE	
TEST	FROM	TO	TOTAL		CORR.		CUM		CUM
None									

CLIENT OLIVER GOLD CORP.
PROPERTY FAIRVIEW

LOCATION SILVER CROWN
SECTION B500N
LATITUDE 8937.83N
DEPARTURE 11164.97E
ELEVATION 748.02m
CORE NQ
LOGGED BY R.J. Beckett

HOLE NO. SC94 - 32
AZIMUTH 222°
DIP -57°
LENGTH 38.4m
PURPOSE Test MV above 94-1
STARTED Dec. 7, 1994
COMPLETED Dec. 7, 1994

METRES		DESCRIPTION	CORE SAMPLES						AVERAGES	
FROM	TO		NUMBER	FROM (m)	TO (m)	WIDTH (m)	Au (OPT)	Ag (OPT)	Au, Ag - width (OPT) (m)	
		STORAGE: Fairview Core Shack								
		HEIGHT OF CASING ABOVE GROUND: 0.2m								
0	3.7	CASING								
3.7	20.7	BIOTITIC CHLORITIC QUARTZITE (UNIT 2) Medium brown-grey, light grey; finely irregularly laminated 1-5mm, locally massive; 70% quartz, 15% biotite, 15% chlorite, minor irreg. 1/2-2mm blebs & stringers pyrite. (3.7 - 7.2) limonitic fractures. (11.8 - 12.0) 16cm quartz vein; white, medium grey, locally banded, 2% disseminated pyrite, upper contact @ 50°. (Hanging Wall Vein Splay) (13.5) 1-2cm cream quartz stringers. (14.0 - 15.0) mafic dyke; dark grey-brown, fine-grained with 20% 2mm subhedral feldspar phenocrysts, contacts sheared. (17.8) very irreg. 3-7mm quartz stringers & brown chloritic bands. (20.5 - 20.7) light brown-grey, bleached, 3% pyrite blebs.	66866	11.8	12.0	0.2	0.100	0.37		
20.7	21.9	QUARTZ VEIN (Hanging Wall Vein Splay) White, light grey-green, medium-grained; massive white quartz with light green fine-grained, finely irregularly laminated silicified quartzite; sparse discontinuous black wispy stylolites, contacts irreg. @ 60°; 1% disseminated pyrite, sparse pyrite on and adjacent to stylolites, locally 2-3mm stringers. (21.1 - 21.5) light grey-green, silicified altered wallrock with quartz blebs, 5% disseminated pyrite.	66867	20.2	20.7	0.5	0.003	0.02		
			66868	20.7	21.1	0.4	0.025	0.21		
			66869	21.1	21.5	0.4	0.011	0.08		
			66870	21.5	21.9	0.4	0.008	0.03	0.015, 0.11 - 1.2m	
21.9	33.1	GRAPHITIC SERICITIC QUARTZITE (UNIT 3) Dark grey, locally light grey-greenish grey, fine- to medium-grained, moderately foliated to massive, foliation @ 45-75°; 70% quartz, 15% sericite, 10% graphite, 5% chlorite, 2% disseminated pyrite, occasional 1-5mm white quartz stringers. (22.8 - 23.8) Medium grey-green, moderately laminated mafic, very irreg. 1/2-2cm quartz stringers. (23.8 - 24.1) white quartz	66871	21.9	22.4	0.5	0.001	< 0.02		
			66876	23.8	24.1	0.3	< 0.001	< 0.02		

DIAMOND DRILL HOLE LOG

FOOTAGE				DIP TESTS		LATITUDE	DEPARTURE	
TEST	FROM	TO	TOTAL		CORR.	CUM	CUM	CUM
1	78.0m				-54°			

CLIENT OLIVER GOLD CORP.
 PROPERTY FAIRVIEW

LOCATION WINDER 2 HOLE NO. SC94 - 33
 SECTION B&ZDN AZIMUTH 222°
 LATITUDE 8240.77N DIP -54°
 DEPARTURE 11207.75E LENGTH 78.0m
 ELEVATION 746.13m PURPOSE Test DN & HWY between 94-17
 CORE NQ STARTED Dec. 8, 1994 & 94-12
 LOGGED BY R.J. Beckett COMPLETED Dec. 9, 1994

METRES		DESCRIPTION	CORE SAMPLES						AVERAGES
FROM	TO		NUMBER	FROM (m)	TO (m)	WIDTH (m)	Au (OPT)	Ag (OPT)	
		STORAGE: Fairview Core Shack							
		HEIGHT OF CASING ABOVE GROUND: 0.3m							
0	3.0	CASING							
3.0	27.7	SERICITIC QUARTZITE (UNIT 3)							
		Light grey, fine- to medium-grained, finely to moderately laminated, foliation @ 80°, sparse irreg. white quartz stringers, occasional 1-5mm blebs pyrite with 1% disseminated pyrite. Lower contact gradational over 50cm.							
		(3.0 - 10.6) limonitic fractures.							
		(9.2 - 11.3) dark grey, finely laminated chert.							
		(13.5) 5cm white quartz vein & wallrock breccia, graphitic slickensides @ 80°.							
		(14.4 - 15.1) broken core.							
		(16.3 - 16.8) quartz/wallrock breccia & irreg. quartz stringers, 5mm kaolin bleb.							
		(16.8 - 17.8) Mafic dyke; light grey, clay-altered, pyritic, @ 80° to C.A.							
		(21.4 - 22.0) irreg. 3-7mm white quartz stringer @ 0°.							
		(22.8 - 23.7) broken core, quartz-pyrite-kaolin stringers, irreg. @ 0-60°.							
		(26.4 - 27.0) tight folds; finely laminated, cherty, 5% 1-3mm pyrite blebs.							
27.7	38.8	MASSIVE QUARTZITE (UNIT 3)							
		Medium grey, fine-grained, massive to weakly laminated locally; 90% quartz, 5% chlorite, 5% sericite, 2% pyrite, disseminated 1-3mm blebs and coating fractures, sparse irreg. white 1-3mm quartz stringers, core broken 10-40cm.							
		(28.2 - 28.9) broken core, irreg. quartz stringers & clayey fractures.							
		(29.3) slickensides @ 55°, 3mm black clay gouge.							
		(35.4) foliated sericitic quartzite, foliation @ 0-20°, fold nose.							
		(36.6) foliated quartzite, tight irreg. folds.							
		(37.3 - 38.2) Breccia; 60% 1-10mm quartzite fragments, subangular, in white quartz matrix.	66882	37.3	38.2	0.9	0.001	0.03	

METRES		DESCRIPTION	CORE SAMPLES							AVERAGES Au, Ag - width (OPT) (m)			
FROM	TO		NUMBER	FROM	TO	WIDTH	Au	Ag					
38.8	43.5	(38.2 - 38.8) black, plastic graphitic gouge, quartz fragments, @ 90°. SERICITIC QUARTZITE (UNIT 3) Black, medium grey, medium grey-brown; fine-grained, finely laminated, foliation @ 70-85°; 80% quartz, 10% sericite, 5% biotite, 2% disseminated pyrite; occasional 5-10cm band black siliceous laminated argillite.	66883	38.2	38.8	0.6	0.008	0.12					
43.5	44.5	QUARTZ VEIN (Hanging Wall Vein) White, 30% dark grey pyritic silicified wallrock fragments with indistinct outlines; medium-grained, massive, indistinct brecciated texture; 3-7% pyrite, disseminated, 10-20% pyrite in dark grey quartz & quartzite sections; black pyritic, stylolites over 5cm at lower contact.	66878	43.0	43.5	0.5	0.005	0.03					
44.5	57.7	CHLORITIC SERICITIC QUARTZITE (UNIT 3) Dark, light grey-brown, dark grey; fine- to very fine grained; moderately laminated 1-7mm with wispy sericitic lamellae & 3-7mm quartz bands; 85% quartz, 10% sericite, 5% chlorite; foliation @ 60°. Lower contact gradational over 20cm. (53.6 - 54.4) broken core, 1/2-2cm. Irreg. 1-3cm white quartz veinlets @ 0-60° & 2mm pyrite stringers at 53.6m. (54.3 - 55.3) Medium green, chloritic foliation planes and blebs; black argillite & irreg. white quartz veins & 1-2mm pyritic stringers below 55.0m.	66879	43.5	44.0	0.5	0.025	0.06					
			66880	44.0	44.5	0.5	0.104	0.05					0.065, 0.06 -1.0
57.7	68.1	CALCAREOUS SILICEOUS TUFF Dark to medium green, light green, fine-grained, finely laminated 1-7mm, banded 2-10cm; very hard to moderately hard; quartz, biotite-chlorite-amphibole, 1-10mm calcite bands; foliation 60-70°; sparse 3-10mm light grey quartz veins parallel foliation; 1% disseminated pyrite; core broken 10-30cm. (66.1 - 68.1) 60% calcite lamellae & as matrix with 40% fragments.	66881	44.5	45.0	0.5	0.027	0.02					
68.1	71.6	QUARTZ VEIN (Main Vein) White, black, dark grey; medium-grained; massive, coarsely banded, stylolitic; in part 1/3 stylolites & dark grey bands spaced 1/2-3cm @ 80°; 2% pyrite predominantly at or adjacent stylolites & dark grey bands, 1% galena as wispy fracture coating & 1/2-3mm blebs, 1% sphalerite as wispy blebs, less than 1/2% chalcopryrite 1/10-1mm blebs; upper contact sharp @ 80°, lower contact broken. (68.5 - 68.8) 20% 2-7mm wispy black stylolites, pyritic. (68.8) 10cm black band, 30% irreg. quartz stringers. (69.2 - 69.7) 2-3% pyrite, disseminated, irreg. stringers and blebs to 3mm. 1-2% very fine grains disseminated galena and blebs to 2mm, locally 2-3% galena as larger blebs and irreg. fracture fillings, 1% light brown and reddish brown sphalerite blebs to 1mm, trace chalcopryrite blebs and very fine grain native gold adjacent to 3mm galena-pyrite aggregate in grey quartz at 69.23m.	66884	55.0	55.3	0.3	0.009	0.10					
			66885	67.6	68.1	0.5	0.001	0.02					
			66886	68.1	68.5	0.4	0.004	0.04					
			66887	68.5	68.8	0.3	0.071	0.23	0.077				
			66888	68.8	69.2	0.4	0.030	0.08					
			66889	69.2	69.7	0.5	0.633	5.12					0.113, 0.92 - 3.5

METRES		DESCRIPTION	CORE SAMPLES								AVERAGES Au, Ag - width (OPT) (m)		
FROM	TO		NUMBER	FROM	TO	WIDTH	Au (OPT)	Ag (OPT)					
		(46.4) 4cm graphitic gouge @ 90°.		(m)	(m)	(m)	(OPT)	(OPT)					
		(48.7 - 52.8) light grey to grey-brown, massive, wispy pyritic stringers, 3% pyrite, 1-3mm irreg. white quartz stringers.											
		(56.0) 20cm black crumbly graphitic gouge & crushed quartz vein @ 55°.											
		(58.4) wispy graphitic lamellae over 12cm.											
59.1	64.1	ARGILLACEOUS GRAPHITIC QUARTZITE Black, grey-brown, light grey; fine-grained, finely laminated, moderately banded, foliation @ 60-80°; short sections of biotitic chloritic quartzite and sericitic quartzite.											
		(59.6) 20cm crumbly graphitic gouge, slickensides @ 80°.											
		(62.7 - 64.0) light grey sericitic quartzite.											
		(63.7 - 64.1) broken core.	66897	63.6	64.1	0.5	<0.001	< 0.02					
64.1	66.8	QUARTZ VEIN (Hanging Wall Vein) White, medium-grained, massive; black stylolites spaced 2-30cm @ 65-70°; quartz indistinctly brecciated & healed by clear quartz & white quartz stringers 1/2-2mm; sparse sulphides, concentrated near stylolites; 1% pyrite, less than 1/2% galena, sphalerite, chalcocopyrite, as 0.1-1mm grains.	66898	64.1	64.7	0.6	0.288	3.44					
		(64.4) 5cm black graphitic quartzite relict fragment.											
		(64.7 - 64.9) laminated black quartz - relict graphitic quartzite @ 60°, 5% pyrite	66899	64.7	64.9	0.2	0.127	1.24					
		(66.2 - 66.8) dark grey quartz with white quartz stringers; 3% pyrite as 1-3mm grains & galena in main white quartz vein at contact.	66900	64.9	66.2	1.3	0.061	0.84					
			66901	66.2	66.8	0.6	0.042	0.63					
66.8	74.3	SERICITIC QUARTZITE (UNIT 3) Light greenish-grey, light grey; fine-grained; well laminated, moderately banded, foliation @ 45-55°; 85% quartz 1-5mm lamellae, 15% sericite 0.1-2mm lamellae, 1% disseminated pyrite; 5% white siliceous bands 3-20mm subparallel fol.	66902	66.8	67.3	0.5	0.002	0.03					
		(68.0) 20cm broken core & irreg. quartz stringers.											
		(70.5 - 71.1) broken core.											
		(71.1 - 71.4) 25cm quartz-wallrock breccia & chloritic gouge; 70% fragments cemented by cream-vuggy quartz; irreg. 1-3mm pyritic stringers @ 35°.	66903	73.8	74.3	0.5	0.002	0.02					

0.112, 1.40 - 2.7

METRES		DESCRIPTION	CORE SAMPLES							AVERAGES			
FROM	TO		NUMBER	FROM	TO	WIDTH	Au	Ag					
74.3	75.2	<p>QUARTZ VEIN (Hanging Wall Vein Splay)</p> <p>White, medium-grained, massive, fractured & rehealed by clear-white quartz stringers, 80% fragments, 20% matrix; 1cm grey stylolitic, pyritic quartz vein at lower contact @ 70°; upper contact @ 75°; 1% pyrite concentrated near dark grey quartz & stylolites, less than 0.5% galena coating stylolites.</p> <p>(74.7) 10cm dark grey quartz, graphitic slip, 3% 1-2mm pyrite grains.</p>		(m)	(m)	(m)	(OPT)	(OPT)					
			66904	74.3	74.6	0.3	0.124	1.46					
			66905	74.6	74.8	0.2	0.002	0.03					
			66906	74.8	75.2	0.4	0.004	0.05					0.044, 0.52 - 0.9
75.2	89.0	<p>SERICITIC QUARTZITE (UNIT 3)</p> <p>Light grey, medium brownish grey, fine-grained; finely laminated, well banded with quartz lamellae 1-20mm and sericitic lamellae 1/2-1mm; 85% quartz, 15% sericite, foliation @ 65-75°.</p> <p>(75.2 - 76.5) black, graphitic argillaceous chert; finely laminated; 20% 1/2-2mm quartz stringers.</p> <p>(76.5 - 77.9) very finely laminated, 30% sericite, tight folds</p> <p>(81.0 - 82.1) broken core.</p> <p>(81.1) very irreg. quartz stringers & wallrock breccia.</p> <p>(83.3) 30cm broken core.</p> <p>(84.5 - 87.1) distinctly banded, 1/2-3cm dark grey-brown quartz bands, foliation @ 60°.</p> <p>(87.5 - 89.0) contorted foliation, irreg. quartz stringers 2-30mm & chloritic quartz vein breccia.</p>											
			66907	75.2	75.7	0.5	0.004	0.06					
89.0	98.0	<p>CALCAREOUS CHLORITIC MAFIC TUFF</p> <p>Dark grey-green; fine-grained; finely laminated 1-5mm, occasional cm-scale bands; chlorite-amphibole-quartz-feldspar, occasional 1/2-1cm calcite bands; 3% irreg. 1-5mm white quartz stringers; foliation @ 75-85°; core broken 10-50cm.</p> <p>(94.5 - 98.5) dark grey-black, weakly laminated graphitic argillaceous chert, 3% 1/2-1cm irreg. quartz stringers, graphitic slips, local contorted foliation and cm-scale folds. 0.9m ground core at 95.8m.</p>											
			66908	95.7	97.0	1.3	0.011	0.17					
			66909	97.0	97.5	0.5	<0.001	0.06					
			66910	97.5	98.0	0.5	0.002	0.14					
98.0	99.0	<p>QUARTZ VEIN (Main Vein)</p> <p>White, dark grey, black; medium-grained; white vein quartz with 30% dark grey to black quartz & graphitic wallrock argillite; stylolitic; 3% 0.1-2mm subhedral grains pyrite concentrated near stylolites & in dark grey quartz; less than 0.5% 0.1-0.5mm blebs sphalerite and galena; vein indistinctly fractured and rehealed with light grey quartz; stylolites and wallrock foliation @ 75-80°, lower contact graphitic.</p>											
			66911	98.0	98.5	0.5	0.006	0.10					
			66912	98.5	99.0	0.5	0.066	1.80					0.036, 0.95 - 1.0

DIAMOND DRILL HOLE LOG

FOOTAGE				DIP TESTS		LATITUDE		DEPARTURE	
TEST	FROM	TO	TOTAL	DIP	CORR.	CUM	CUM	CUM	CUM
1	115.8m			-61°					

CLIENT OLIVER GOLD CORP.
 PROPERTY FAIRVIEW

LOCATION WINDER 2 HOLE NO. SC94 - 35
 SECTION 8440N (8443N *) AZIMUTH 222°
 LATITUDE 8939.54N DIP -63°
 DEPARTURE 11242.89E LENGTH 115.8m
 ELEVATION 742.38m PURPOSE Test below 94-13
 CORE NO. STARTED Dec. 10, 1994
 LOGGED BY R.J. Beckett COMPLETED Dec. 11, 1994

METRES		DESCRIPTION	CORE SAMPLES							AVERAGES
FROM	TO		NUMBER	FROM	TO	WIDTH				
		STORAGE: Fairview Core Shack								
		HEIGHT OF CASING ABOVE GROUND: 0.2m								
0	3.0	CASING								
3.0	39.9	SERICITIC QUARTZITE (UNIT 3)								
		Light grey, grey-brown, minor dark grey; fine-grained; finely laminated 1/2-5mm moderately banded to 1cm, occasionally massive, foliation @ 75-85°; 85% quartz, 15% sericite, minor biotitic or graphitic sections 1/2-3m; core broken 10-30cm parallel foliation, minor quartz, clay, & pyrite coated fractures @ 40-70°.								
		(3.0 - 7.5) limonitic fractures, 2m ground core.								
		(8.5 - 12.8) dark grey, graphitic, argillaceous, wispy lamellae 3-10mm; graphitic slip @ 65° at 10.9m.								
		(16.9 - 20.1) broken core, 1-3mm clayey quartz stringers.								
		(21.1 - 23.5) 95% quartz, finely laminated to massive; wispy black chloritic(?) hairline fractures @ 90° to foliation.								
		(26.7) 3cm crumbly gouge @ 75°, parallel foliation.								
		(29.5 - 32.1) 95% quartz, wispy chloritic/sericitic lamellae.								
		(34.0 - 35.0) Intermediate tuff; brown, green-grey, fine-grained, irreg. finely laminated.								
		(38.3 - 39.1) Intermediate tuff; dark grey-green, fine-grained, massive, wispy green irreg. bands.								
39.9	53.9	BIOTITIC QUARTZITE (UNIT 2)								
		Dark grey-brown, fine- to very fine grained, finely laminated, moderately banded 1/2-2cm; 95% quartz, 5% biotite, trace sericite & chlorite as indistinct laminations, sparse irreg. 1-3mm white and grey quartz stringers @ 0-40°, 2% disseminated pyrite; contacts gradational.								
		(44.1) 1cm graphitic gouge @ 85°.								
		(45.7 - 46.0) broken core.								
		(50.1 - 51.6) black, finely laminated, graphitic, argillaceous quartzite.								

* Hole drilled 3m north of section due to thick timber.

METRES		DESCRIPTION	CORE SAMPLES										
FROM	TO		NUMBER	FROM (m)	TO (m)	WIDTH (m)	Au (OPT)	Ag (OPT)					AVERAGES
53.9	59.0	SERICITIC QUARTZITE (UNIT 3) Light grey, light brown-grey; fine-grained; moderately laminated with 2-5mm quartz laminae and 1-3mm sericite laminae; 20% irreg. 1/2-3cm quartz bands, minor 3-5cm graphitic bands; foliation @ 70°. (50.6 - 56.0) 3% irreg. white quartz stringers @ 0-30°.											Au, Ag - width (OPT) (m)
59.0	65.3	BIOTITIC CHLORITIC QUARTZITE (UNIT 2) Medium to dark brown-grey to dark grey; fine-grained; moderately banded and laminated; 85% quartz, 10% chlorite, 5% biotite, minor graphite locally; foliation @ 65-75°. (62.8 - 62.9) 7cm grey quartz vein @ 75-90°, 2mm irreg. pyrite stringer. (63.3 - 63.8) broken core, sericitic. (65.1) 10cm quartz breccia & quartz stringers; upper contact @ 20°.	66915	62.8	62.9	0.1	<0.001	<0.02					
65.3	65.9	FAULT ZONE Black, greenish grey; crumbly clay gouge 35cm @ 90°, graphitic slickensides, gouge & quartz wallrock fragments to 5mm; upper contact along graphitic slips @ 35°, lower contact on graphitic gouge @ 65°.											
65.9	69.1	SERICITIC QUARTZITE (UNIT 3) Light grey, brownish grey; fine-grained; moderately laminated, foliation @ 75-85°; 2% disseminated pyrite.	66916	68.6	69.1	0.5	0.006	0.07					
69.1	73.0	QUARTZ VEIN (Hanging Wall Vein - Upper Part) 50% massive white quartz vein, 30% white, dark grey, black banded & stylolitic quartz, 20% silicified finely laminated sericitic quartzite/chert; banding @ 60-85°; sulphides in white vein quartz: sparse 1/2-3mm blebs subhedral pyrite, less than 1/2% sphalerite as 1/2-2mm blebs and wispy galena on discontinuous fractures, less than 1/2% chalcopryrite as 1-2mm blebs; sulphides in grey banded quartz: 5% pyrite disseminated & irreg. 1-3mm patches, 1% galena as less than 1mm blebs & coating fractures & stylolites & as very fine grains in "dusty" patches, less than 1/2% sphalerite, 1/2% chalcopryrite; upper contact @ 40°, lower @ 85°. (69.5 - 69.7) 40% white quartz subangular fragments in dark grey quartz, pyritic. (70.6 - 71.0) banded white-dark grey, stylolitic; discontinuous 1-5mm pyritic stringers @ 90°. (71.0 - 71.4) 60% greenish grey silicified wallrock, 40% quartz vein; 1-3mm pyritic stringers at quartz vein contact. (71.4 - 71.7) banded grey to dark grey quartz, stylolitic, 7% pyrite, 1% galena, sphalerite and chalcopryrite. (71.7 - 73.0) massive white quartz, minor pyrite, chalcopryrite, sphalerite.	66917	69.1	69.5	0.4	0.027	0.46					
			66918	69.5	69.9	0.4	0.137	1.94					
			66919	69.9	70.6	0.7	0.338	0.82					0.265, 1.23 - 1.1
			66920	70.6	71.0	0.4	0.31	0.14					0.108, 0.95 - 3.9
			66921	71.0	71.4	0.4	0.009	0.06					
			66922	71.4	71.7	0.3	0.097	1.61					
			66923	71.7	72.4	0.7	0.095	2.10					
			66924	72.4	73.0	0.6	0.014	0.20					

METRES		DESCRIPTION	CORE SAMPLES								AVERAGES Au, Ag - width (OPT) (m)		
FROM	TO		NUMBER	FROM (m)	TO (m)	WIDTH (m)	Au (OPT)	Ag (OPT)					
73.0	77.6	SERICITIC QUARTZITE (UNIT 3) Light grey, medium grey, black; fine-grained; moderately foliated @ 70°; 90% quartz, 10% sericite, minor graphite locally. (76.9 - 77.2) grey chloritic bands in graphitic argillite.	66925	73.0	73.5	0.5	0.003	0.03					
			66926	76.9	77.6	0.7	<0.001	0.02					
77.6	81.7	QUARTZ VEIN (Hanging Wall Vein - Lower part) Massive white quartz vein, 3% irreg. white quartz stringers, 3% 1-7mm irreg. blebs pyrite, 2% galena as wispy irreg. discontinuous patches & fracture coatings, less than 1/2% sphalerite and chalcopryrite. (78.3 - 78.6) grey laminated quartzite.	66927	77.6	78.3	0.7	0.013	0.21					
		(79.1 - 80.1) 7% coarse-grained pyrite, galena as wispy fracture coatings & 1-2mm blebs.	66928	78.3	78.6	0.3	0.033	0.50					
		(80.1 - 81.7) massive white quartz, indistinct grey patches of fine-grained dis- seminated pyrite, minor pyrite blebs, minor fine-grained sphalerite & chalco- pyrite.	66929	78.6	79.1	0.5	0.062	0.76					
		(81.6) grey quartz, 3% pyrite, very fine grained galena, minor blebs 1/2-1mm sphal- erite, contacts @ 40°.	66930	79.1	79.6	0.5	0.039	0.27					
			66931	79.6	80.1	0.5	0.045	0.56					
			66932	80.1	80.6	0.5	0.053	0.14					
			66933	80.6	81.1	0.5	0.055	0.59					
			66934	81.1	81.7	0.6	0.012	0.21					
81.7	83.9	GRAPHITIC QUARTZITE Dark grey, medium grey; fine-grained, finely to moderately laminated 1-5mm, foliation @ 55°, locally folded and contorted, graphitic. (81.7 - 82.0) breccia; quartzite fragments in quartz matrix, 5% pyrite. (82.2) tight cm-scale folds over 30cm.	66935	81.7	82.3	0.6	0.003	0.02					
			66936	82.3	82.6	0.3	0.014	0.14					
			66937	82.6	83.1	0.5	0.004	0.03					
83.9	92.4	SERICITIC QUARTZITE (UNIT 3) Light grey, fine-grained, well banded, quartz 2-15mm, sericite 1/2-2mm layers; foliation @ 65°, core broken 1-10cm, irreg. clayey quartz stringers @ 0-20°. (89.5 - 92.4) brown-grey, distinctly banded chert.											
92.4	100.9	CALCAREOUS INTERMEDIATE TUFF Grey-green, light green, white; finely laminated, well banded 1-20mm; calcar- eous matrix in part & 5% 1-7mm calcite bands, chloritic, siliceous intermediate to mafic tuff, occasional white quartz stringers; foliation @ 60°. (99.4 - 100.9) very finely laminated 1/2-2mm, grey to dark grey chert.	66938	100.4	100.9	0.5	<0.001	0.03					

0.035, 0.39 - 4.1

DIAMOND DRILL HOLE LOG

LOCATION JINDO 2
 SECTION 8425N
 LATITUDE 8921.29N
 DEPARTURE 11251.04E
 ELEVATION 743.71m
 CORE NO. _____
 LOGGED BY R.J. Bockett

HOLE NO. SC94 - 36
 AZIMUTH 222°
 DIP -63°
 LENGTH 102.4m
 PURPOSE Test south of 94-13
 STARTED Dec. 12, 1994
 COMPLETED 1st. 13, 1994

FOOTAGE			DIP TESTS		LATITUDE		DEPARTURE	
TEST	FROM	TO	TOTAL	DIP	COGR.	CUM	CUM	CUM
1	102.0m			-60				

CLIENT OLIVER GOLD CORP.
 PROPERTY FAIRVIEW

METRES		DESCRIPTION	CORE SAMPLES							AVERAGES
FROM	TO		NUMBER	FROM	TO	WIDTH	Au	Ag		
				(m)	(m)	(m)	(OPT)	(OPT)		
		STORAGE: Fairview Core Shack								
		HEIGHT OF CASING ABOVE GROUND: 0.1m								
0	3.0	CASING								
3.0	48.9	CHLORITIC SERICITIC QUARTZITE (UNIT 3)								
		Medium grey-brown, medium grey, light grey; fine-grained; moderately to finely banded, finely laminated, foliation @ 65-75°; 5-30cm sections dark-medium grey-brown to dark grey, laminated 1-3mm; 1% disseminated fine-grained pyrite; core broken 10-50cm parallel foliation.								
		(3.0 - 7.3) limonitic fractures.								
		(10.7 - 17.7) very broken core; 0.9m ground core.								
		(17.8 - 21.5) black graphitic bands ¼-10cm, graphitic slips parallel foliation.								
		(22.4 - 29.3) medium grey-brown, massive, 95% quartz with fine-grained disseminated biotite.								
		(30.5 - 31.3) tight folds in laminae - fold nose; wispy ¼mm pyritic chloritic stringers subparallel foliation.								
		(31.9) 1-2cm quartz stringers over 25cm; broken core.								
		(32.6 - 33.0) Mafic dyke; green-grey to grey-brown, fine-grained, massive, contact parallel foliation.								
		(35.5 - 36.6) Mafic dyke/sill; grey-green, fine-grained, massive, irreg. quartz stringers @ 10°, to 5mm.								
48.9	54.4	SERICITIC QUARTZITE (CHERT) (UNIT 3)								
		Medium grey, light grey sericitic quartzite, minor dark grey chloritic sericitic quartzite; laminated 1-3mm; numerous tight to open cm-scale folds, axial planes @ 90° to core; sparse vuggy quartz stringers with minor calcite & pyrite; wispy black discontinuous pyritic & chloritic stringers ¼-1mm.								
		(49.5) 20cm crushed rock & white kaolin stringers.								
54.4	56.4	QUARTZ BRECCIA								
		Light grey, coarse-grained, massive breccia; 60% 1-7mm quartzite fragments in white quartz matrix; lower contact at 5cm clay gouge @ 20°.	66944	54.4	55.4	1.0	<0.001	<0.02		
			66945	55.4	56.4	1.0	0.005	<0.02		

METRES		DESCRIPTION	CORE SAMPLES											
FROM	TO		NUMBER	FROM	TO	WIDTH	Au	Ag	Au**	** Screened for metallics	AVERAGES			
			(m)	(m)	(m)	(OPT)	(OPT)	(OPT)						
56.4	67.8	SERICITIC QUARTZITE (UNIT 3) Light grey, medium grey fine-grained, laminated 1-3mm occasionally massive, foliation @ 55-65°; sericitic quartzite with 5-30cm black graphitic sections, graphitic slickensides; 1% disseminated pyrite throughout. (58.1 - 59.0) clay gouge & quartz breccia @ 5°. (59.3) 3cm graphitic gouge & slickensides @ 60°. (62.9) 30cm graphitic quartzite, graphitic argillite, 15cm foliated green clay gouge. (63.3) 3cm black graphitic gouge & slickensides @ 60°. (64.7) irreg. 1-3mm pyritic stringers over 12cm.	66946	66.8	67.3	0.5	<0.001	<0.02						
			66947	67.3	67.8	0.5	0.008	0.46						
67.8	69.4	QUARTZ VEIN (Hanging Wall Vein) White, grey, medium- to coarse-grained; coarsely banded to massive; yellow & black sulphidic, stylolitic quartz & black graphitic argillite & graphitic quartzite bands. (67.8 - 68.4) white quartz vein & black graphitic quartzite @ 80°; 2% disseminated pyrite. (68.4 - 68.9) graphitic quartzite, 3% pyrite. (68.9 - 69.4) grey quartz & black graphitic stylolites @ 90°; 5% coarse 1-5mm pyrite, 3% coarse blebs chalcopyrite, 3% galena as fine dustings, fracture fillings and coarse aggregates to 4mm, 1-2% brown sphalerite as fine grains and rarely aggregates to 2mm, native gold as 0.1-mm blebs and a fine seam in upper 10cm of section.	66948	67.8	68.4	0.6	0.044	0.65						
			66949	68.4	68.9	0.5	0.018	0.32						
			66950	68.9	69.4	0.5	7.152	4.56	8.827				2.000, 1.29 - 2.3	
69.4	75.3	SERICITIC & GRAPHITIC QUARTZITE (UNIT 3) with QUARTZ VEIN ZONES (69.4 - 71.9) siliceous light grey quartzite, irreg. 2-20cm white quartz veins. (71.9 - 73.1) grey laminated quartzite, graphitic in part, 10cm graphitic breccia. (73.1 - 73.8) white quartz vein, stylolitic, occasional 1-3cm graphitic slickensides argillite, foliation @ 75°, 2% disseminated pyrite. (73.8 - 74.6) grey laminated quartzite & graphitic quartzite, occasional 1-2cm sections of crushed rock & graphitic slickensides. (74.6 - 75.3) quartzite with irreg. white quartz stringers, 2% disseminated pyrite, upper contact @ 40°, lower contact @ 60°.	66951	69.4	70.1	0.7	0.216	0.19						
			66952	70.1	70.9	0.8	0.005	0.03						
			66953	70.9	71.9	1.0	0.007	0.02						
			66954	71.9	73.1	1.2	0.051	0.06						
			66955	73.1	73.8	0.7	0.003	0.02						
			66956	73.8	74.6	0.8	0.020	0.32						
			66957	74.6	75.3	0.7	0.049	0.84						
75.3	82.5	SERICITIC QUARTZITE (UNIT 3) Light grey, minor medium to dark grey; fine-grained; weakly banded, laminated 1-5mm; 85% quartz, 15% sericite; foliation @ 65-85°; occasional 1/2-1cm discontinuous quartz bands.	66958	75.3	75.8	0.5	0.006	0.08						

DIAMOND DRILL HOLE LOG

FOOTAGE				DIP		LATITUDE		DEPARTURE	
TEST	FROM	TO	TOTAL		CORR.	CUM		CUM	
None									

CLIENT OLIVER GOLD CORP.

PROPERTY FAIRVIEW

LOCATION SILVER CROWN
 SECTION 8530N
 LATITUDE 8955.76N
 DEPARTURE 11163.10E
 ELEVATION 749.56m
 CORE NQ
 LOGGED BY R.J. Beckett

HOLE NO. SC94 - 37
 AZIMUTH 222°
 DIP -46°
 LENGTH 28.2m
 PURPOSE Test MV above 94-2
 STARTED Dec. 13, 1994
 COMPLETED Dec. 13, 1994

METRES		DESCRIPTION	CORE SAMPLES						AVERAGES
FROM	TO		NUMBER	FROM (m)	TO (m)	WIDTH (m)	Au (OPT)	Ag (OPT)	
		STORAGE: Fairview Core Shack							
		HEIGHT OF CASING ABOVE GROUND: 0.1m							
0	3.0	CASING							
3.0	13.5	CHLORITIC SERICITIC QUARTZITE (UNIT 3)							
		Medium grey, medium-grained, weakly foliated, finely laminated in part @ 60-70°.							
		(3.0 - 6.8) limonitic fractures.							
		(10.3 - 10.5) crumbly grey sandy gouge, slickensides @ 55°.							
		(10.5 - 11.0) 0.2m ground core, white quartz vein fragments.							
		(12.0 - 13.5) dark grey, very hard, massive quartzite; 2% disseminated pyrite. 5cm quartz vein @ 20° at 12.5m, 1% pyrite.							
		(13.3 - 13.5) patchy light grey-green bleached sections; irregular 1-3mm quartz stringers.	66968	13.0	13.5	0.5	0.005	0.11	
13.5	14.4	QUARTZ VEIN							
		White, coarse-grained, massive, sparse indistinct grey patches; 1% pyrite as 1-3mm blebs in quartz vein and in wallrock at vein margin, less than 1/2% galena concentrated over 1cm at lower contact.							
		(14.0) 7cm siliceous quartzite, 3% pyrite.	66969	13.5	14.4	0.9	0.025	0.29	
14.4	19.2	CALCAREOUS MAFIC TUFF							
		Dark green, medium grey, brownish green; fine-grained; finely laminated 1-5mm calcareous - 10% 4-2cm calcite bands.							
		(14.4 - 15.4) dark grey-brown, finely laminated chert.	66970	14.4	14.9	0.5	0.002	<0.02	
		(16.7) 2cm chloritic gouge & carbonate stringers @ 50°.							
		(18.7 - 18.9) broken core.							
19.2	24.4	CHLORITIC QUARTZITE (UNIT 2)							
		Dark grey, light grey, greenish grey; medium-grained; weakly foliated; laminated to massive; foliation @ 50-60°.							

DIAMOND DRILL HOLE LOG

DIP TESTS									
TEST	FOOTAGE			DIP		LATITUDE		DEPARTURE	
	FROM	TO	TOTAL	COSE	CUM	CUM	CUM	CUM	
1	64.0m			-47°					

CLIENT OLIVER GOLD CORP
PROPERTY FAIRVIEW

LOCATION WINDER 2
SECTION 8515N
LATITUDE 8268.86N
DEPARTURE 11172.11E
ELEVATION 745.30m
CORE NO
LOGGED BY R.J. Beckett

HOLE NO. SC94 - 38
AZIMUTH 222°
DIP 50°
LENGTH 64.0m
PURPOSE Test between 94-1 & 94-2
STARTED Dec. 13, 1994
COMPLETED Dec. 15, 1994

METRES		DESCRIPTION	CORE SAMPLES						AVERAGES
FROM	TO		NUMBER	FROM (m)	TO (m)	WIDTH (m)	Au (OPT)	Ag (OPT)	
		STORAGE: Fairview Core Shack							
		HEIGHT OF CASING ABOVE GROUND: 0.2m							
0	6.1	CASING							
6.1	19.6	SERICITIC QUARTZITE (UNIT 3)							
		Light grey, fine-grained, weakly foliated to massive; 80-98% quartz, 20-0% sericite, 1-2% disseminated pyrite & fracture coatings, sparse 1-3mm blebs & stringers; locally finely laminated, foliation @ 75-85°.							
		(6.1 - 8.1) limonitic fractures.							
		(9.1 - 10.5) light grey quartz stringers 3-5cm, irreg. @ 10-40°.							
		(10.0 - 11.0) broken core, 20cm ground core.							
		(11.0 - 12.4) tight cm-scale folds - fold nose.							
		(12.7) 1/2-2cm chloritic gouge & 5mm pyritic stringers.							
		(12.8) 40cm broken core.							
		(14.9 - 16.8) 95% medium grey quartz & indistinct shreds 1-5mm sericitic quartzite, 2% pyrite as irreg. 3mm blebs and stringers and fracture coatings; 5% 1-3mm irreg. white quartz stringers, vuggy.							
		(16.8 - 17.8) finely laminated dark grey graphitic sericitic quartzite.							
		(17.8 - 18.6) Porphyritic felsic dyke, clay-altered, slickensides @ 40°.							
		(19.2 - 19.6) Mafic dyke; light grey, massive, clay-altered, upper contact sharp @ 90°, 2cm clay gouge.							
19.6	24.2	FAULT ZONE							
		Breccia - 70% light grey, 1-20mm quartzite fragments, subangular, in white vuggy quartz matrix.							
		(21.0 - 22.6) 1.6m ground core.	66975	19.6	22.6	3.0	0.001	< 0.02	
			66976	22.6	23.4	0.8	< 0.001	< 0.02	
			66977	23.4	23.7	0.3	< 0.001	< 0.02	
		(23.7 - 24.2) black crumbly graphitic gouge & crushed quartzite and quartz vein; 3% pyrite, disseminated & 1-3mm blebs; coarsely foliated @ 90°. (This zone may include the Hanging Wall Vein)	66978	23.7	24.2	0.5	0.005	0.08	

METRES		DESCRIPTION	CORE SAMPLES								
FROM	TO		NUMBER	FROM (m)	TO (m)	WIDTH (m)	Au (OPT)	Ag (OPT)	AVERAGES		
24.2	37.6	<p>BIOTITIC CHLORITIC QUARTZITE (UNIT 2)</p> <p>Dark grey, medium grey-brown, fine-grained; moderately laminated 1-5mm, foliation @ 75-85°; 85-95% quartz, 5-15% chlorite, 3-5% biotite; minor graphitic laminated cherty argillite; occasional tight cm-scale folds.</p> <p>(24.4 - 24.6) 20cm tightly folded graphitic cherty argillite.</p> <p>(27.1) irreg. 2-5cm white quartz stringers.</p> <p>(27.3 - 27.7) tight cm-scale folds.</p> <p>(34.6) tight cm-scale folds.</p> <p>(37.2 - 37.6) Mafic dyke or sill; dark green, fine-grained, massive; upper contact parallel foliation @ 80°, lower contact at 5mm chloritic gouge.</p>									
37.6	52.0	<p>CALCAREOUS MAFIC TUFF</p> <p>Dark grey-green, medium green, light grey; fine-grained; well laminated 1-5mm banded 1-5cm; chloritic matrix, calcareous in part, 5% calcite bands 3-10mm, 7% quartz bands 5-20mm, patchy 5-10cm sections with 70% light grey quartz & calcite matrix and anastomosing quartz-carbonate stringers; foliation @ 75-85°; core broken 10-30cm parallel to foliation.</p> <p>(38.9) 15cm quartz-calcite stringers.</p> <p>(39.9 & 42.4) tight cm-scale folds.</p> <p>(43.0 - 43.1) 12cm finely, irreg. laminated light brown quartz-sericite chert, 1-3mm quartz stringers, 5% 1-2mm blebs pyrite.</p> <p>(43.9 - 46.3) grey finely laminated chert-sericite band.</p> <p>(48.1 - 49.3) black, fine-grained siliceous argillite; graphitic foliation plane</p> <p>(49.1 - 49.4) broken core.</p> <p>(51.2 - 51.8) 50% light grey quartz/calcite bands 2-10mm.</p>	66979	43.0	43.1	0.1	0.002	0.08			
52.0	54.3	<p>CHLORITIC TUFF & GRAPHITIC ARGILLITE</p> <p>Black, medium grey, grey-green; fine-grained; weakly laminated, moderately banded, foliation @ 75-85°; mixed sections quartz-banded chloritic tuff and graphitic, quartz-nodule argillite.</p> <p>(52.4 - 52.7) 30cm graphitic argillite with 30% grey quartz nodules 3-7mm; 1cm quartz vein @ 80° at upper contact.</p> <p>(52.7 - 53.0) white quartz vein breccia & black graphitic argillite shreds, white-grey quartz vein fragments.</p> <p>(53.0 - 54.3) 40% chlorite, 30% sericite 30% quartz; moderately irreg. laminated lower contact @ 75°.</p>	66980	52.2	52.7	0.5	<0.001	<0.02			
			66981	52.7	53.0	0.3	0.008	0.12			
			66982	53.0	54.0	1.0	0.004	0.05			
			66983	54.0	54.3	0.3	0.003	<0.02			

METRES		DESCRIPTION	CORE SAMPLES										
FROM	TO		NUMBER	FROM	TO	WIDTH	Au	Ag				AVERAGES	
				(m)	(m)	(m)	(OPT)	(OPT)					
43.2	47.5	(39.5 - 40.9) dark green and light grey blotchy appearance, 1/2-lcm siliceous patches in dark green dyke; minor 2-5mm blebs pyrrhotite in lower 10cm. BIOTITIC QUARTZITE (UNIT 2) Light to medium brown, fine-grained, moderately to finely banded, foliation @ 60-70°; similar to (26.7 - 39.5); broken core 1/2-5cm; 2.8m ground core.	66987	45.7	47.5	1.8	0.001	< 0.02					
47.5	51.2	QUARTZ VEIN & QUARTZ VEIN BRECCIA (Hanging Wall Vein) (47.5 - 50.6) Breccia, 2.7m ground core, only 40cm recovered in section. Breccia: 1-15mm light grey subrounded quartzite fragments in white quartz matrix; white quartz stringers. (50.6 - 51.2) White quartz vein; sparse sulphides except over 1cm above lower contact: 1-3mm blebs pyrite, 1-2mm blebs chalcopyrite and sphalerite, wispy galena.	66988	47.5	50.6	3.1	0.003	< 0.02					
			66989	50.6	51.2	0.6	0.103	1.22					
51.2	61.7	CHLORITIC BIOTITIC QUARTZITE (UNIT 2) Medium to light brown, fine- to very fine grained, moderately laminated to massive; 90% quartz (chert), 7% chlorite, 3% biotite. (51.2 - 53.2) Light grey, massive to weakly foliated quartzite. (53.2 - 55.3) Intermediate sill; dark green, medium-grained; 60% amphibole, 30% feldspar, 10% quartz; lower contact parallel foliation @ 60°. (58.5 - 59.0) broken core. (58.6) 9cm white quartz vein with 40% chloritic wallrock, wispy black stylolites.	66990	51.2	51.8	0.6	0.005	0.08					
			66991	58.6	58.7	0.1	0.004	< 0.02					
61.7	67.8	BIOTITIC QUARTZITE (UNIT 2) Medium grey-brown, fine-grained, moderately foliated @ 45-55°; local wispy black laminae; occasional 10cm bands finely laminated 60% sericite, 40% quartz, 3% pyrite, mm-scale tight folds, 1/2-5mm white quartz stringers; contacts gradational.											
67.8	72.1	CALCAREOUS INTERMEDIATE TUFF Dark green, light green, fine-grained, moderately to well laminated 2-10mm, foliation @ 60°; calcareous intermediate to mafic tuff, chloritic fractures parallel foliation. (70.4 - 71.8) broken core; 0.7m ground core, graphitic slickensides.											
72.1	75.4	CHLORITIC QUARTZITE (UNIT 2) Medium grey, fine-grained, weakly foliated, moderately schistose; 60% quartz, 40% chlorite; finely laminated locally with sericite, chlorite, 3% pyrite. (75.0 - 75.4) broken core.	66992	74.9	75.4	0.5	0.001	0.04					

METRES		DESCRIPTION	CORE SAMPLES											
FROM	TO		NUMBER	FROM (m)	TO (m)	WIDTH (m)	Au (OPT)	Ag (OPT)	AVERAGES					
42.6	43.2	MEDIUM GREY-WHITE QUARTZITE Medium to light grey, white; fine- to coarse-grained, weakly foliated to massive; irreg. wispy black pyrite-chlorite stringers 1/2-1mm; weakly foliated with dark brown to black laminae @ 75°; 5% pyrite as 1-3mm blebs. (43.0 - 43.2) white quartz stringers @ 75°.	66998	42.6	43.0	0.4	<0.001	<0.02						
			66999	43.0	43.2	0.2	0.004	0.04						
43.2	72.3	BIOTITIC QUARTZITE (UNIT 2) Medium grey-brown, medium-grained, moderately foliated @ 75°; 40% 3-7mm quartz bands, irreg. & discontinuous. (44.9 - 46.8) Intermediate sill (Unit 11); black to dark green, fine-grained, massive; coarse irreg. 7-15mm light green blebs & light green bleaching adjacent to black fractures; contacts parallel to foliation. (46.8 - 53.2) massive quartzite; medium grey, fine-grained, mottled light & medium grey; 1% disseminated pyrite, 1% disseminated fine-grained biotite. Lower contact gradational over 2m. (53.2 - 72.3) medium grey-brown to medium grey, fine-grained, weakly to moderately foliated, moderately laminated, foliation @ 70-80°; 85% quartz, 10-15% biotite 0-5% chlorite; occasional dark grey to black, moderately laminated graphitic sections 3-30cm; occasional 1/2-1cm light grey quartz bands parallel to foliation; sparse 1-3mm quartz stringers @ 30-40°. (53.7 - 53.8) light grey, sericitic. (54.6) 7mm pink quartz veinlet @ 35°. (54.7 - 54.9) 18cm brown, fine-grained mafic band, irreg. light grey bleached veins, 2-3mm pyrite blebs. (55.9 - 56.2) dark grey, graphitic, 14mm quartz veinlet parallel foliation. (58.6 - 59.0) black graphitic argillite; graphitic stringers, broken core. (59.6 - 59.7) open fold over 12cm; discontinuous light grey quartz stringers. (61.4 - 61.8) 1-4cm quartz veinlets subparallel foliation @ 70°. (65.4) 5cm graphitic quartzite, irreg. quartz & white clay stringers, graphitic slickensides. (65.5 - 66.2) medium grey sericitic quartzite, irreg. 1-3mm quartz stringers @ 0°. (68.0 - 69.0) dark grey, very fine grained graphitic argillaceous quartzite, chloritic fractures, moderately foliated @ 75°. (70.2 - 70.7) dark grey, moderately laminated graphitic quartzite. (70.7 - 72.3) medium grey to light grey, finely laminated, sericitic; lower contact sharp @ 30°.	67000	43.2	43.6	0.4	0.002	<0.02						

METRES		DESCRIPTION	CORE SAMPLES									
FROM	TO		NUMBER	FROM (m)	TO (m)	WIDTH (m)	Au (OPT)	Ag (OPT)	Au** (OPT)	** Screened for metallics	AVERAGES Au, Ag - width (OPT) (m)	
72.3	76.2	BRECCIA 80% fragments; light grey, 1-20mm, angular, laminated quartz-stringered sericitic quartzite, in grey-white sugary quartz matrix; crumbly graphitic gouge locally; 2% pyrite as occasional 3mm blebs, 1-3mm pyritic stringers at lower contact. (72.3 - 73.8) 0.7m ground core, 10cm crumbly graphitic gouge @ 45° at 73.7m (75.2 - 76.2) very broken core, 60cm ground core.	71601	72.3	73.8	1.5	<0.001	<0.02				
			71602	73.8	74.8	1.0	0.001	0.03				
			71603	74.8	76.2	1.4	0.006	0.04				
76.2	88.2	QUARTZ VEIN ZONE (Hanging Wall Vein) (76.2 - 77.4) white quartz vein & black graphitic quartzite shreds & bands @ 75°, very broken core, 0.7m ground core. (77.4 - 78.2) white-grey quartz vein, irreg. 1-3mm vuggy quartz stringers; 3% pyrite as patchy 0.1-2mm grains & 1-5mm blebs, 1/2-1% sphalerite, chalcopyrite & galena adjacent pyrite blebs, grey dusty sulphidic patches of very fine grained galena; one 0.1mm grain of native gold adjacent grey sulphidic patch; one 5cm fragment of pyritic laminated chert within quartz vein. (78.2 - 78.8) brecciated white quartz in medium to dark grey quartz with irreg. dark grey sulphidic laminae @ 55°. (78.8 - 80.0) Sericitic quartzite; medium grey, light grey, white; moderately laminated, foliation @ 60°, 2% pyrite. (79.9) 3cm dark grey, pyritic, brecciated. (80.0 - 80.7) white quartz vein, wispy dark grey laminae 1-2mm; 15cm pyritic sericitic quartzite; less than 1/2% galena as 1-2mm blebs. (80.7 - 81.9) quartzite breccia with 30% white quartz veins, pyritic & graphitic slickensides @ 45°, grooves @ 80°. (81.9 - 82.9) Chloritic sericitic quartzite (chert); light greenish grey, finely laminated 1-3mm, locally schistose. (82.9 - 83.6) Sericitic quartzite; light grey, white, finely laminated 1-3mm, open fold over 15cm, brecciated locally. (83.6 - 84.4) 50% white-medium grey quartz veins & stringers, wispy 1-2mm grey pyritic bands; 50% light grey sericitic quartzite, 5% pyrite as 1-5mm blebs & irreg. quartz stringers. (84.4 - 87.2) Chloritic sericitic quartzite (chert); medium-light grey, fine- to very fine grained, finely laminated; irreg. cm-scale folds, irreg. 3-10mm white to grey quartz stringers; 1-5% disseminated pyrite; vuggy quartz stringer at lower contact. (87.2 - 88.2) white quartz vein; discontinuous, wispy grey chloritic, graphitic & pyritic laminae 1/2-5mm, laminae @ 55-65°; 3% pyrite as coarse-grained bleb to 1cm & disseminated on laminae; lower contact parallel foliation @ 60°. Initial 30cm broken.	71604	76.2	77.4	1.2	0.078	0.59				
			71605	77.4	78.2	0.8	0.196	0.46	0.116		0.090, 0.48 - 2.6	
			71606	78.2	78.8	0.6	0.078	0.30			0.059, 0.45 - 4.5	
			71607	78.8	80.0	1.2	0.007	0.16				
			71608	80.0	80.7	0.7	0.035	0.83				
			71609	80.7	81.9	1.2	0.003	0.06				
			71610	81.9	82.9	1.0	0.002	<0.02				
			71611	82.9	83.6	0.7	0.008	0.03				
			71612	83.6	84.4	0.8	0.009	0.09				
			71613	84.4	85.2	0.8	0.012	0.09				
			71614	85.2	86.2	1.0	0.009	0.05				
			71615	86.2	87.2	1.0	0.018	0.20				
			71616	87.2	88.2	1.0	0.093	0.60				

DIAMOND DRILL HOLE LOG

LOCATION SILVER CROWN HOLE NO. SC94 - 41
 SECTION 8485N AZIMUTH 222
 LATITUDE 8940.64N DIP -60
 DEPARTURE J1187.76E LENGTH 61.3m
 ELEVATION 744.36m PURPOSE Test between 94-1 & 94-33
 CORE NQ STARTED Dec. 19, 1994
 LOGGED BY R.J. Beckett COMPLETED Dec. 20, 1994

CLIENT OLIVER GOLD CORP.
 PROPERTY FAIRVIEW

FOOTAGE			DIP TESTS		LATITUDE	DEPARTURE
TEST	FROM	TO	TOTAL	CORR.	CUM	CUM
Missing						

METRES		DESCRIPTION	CORE SAMPLES						AVERAGES
FROM	TO		NUMBER	FROM (m)	TO (m)	WIDTH (m)	Au (OPT)	Ag (OPT)	
		STORAGE: Fairview CoFe Shack							
		HEIGHT OF CASING ABOVE GROUND: 0.1m							
0	3.0	CASING							
3.0	21.9	SERICITIC QUARTZITE (UNIT 3)							
		Light grey, fine-grained, well to moderately laminated 1-5mm, 90% quartz wavy, discontinuous laminae, 10% wispy sericite laminae 1-2mm; foliation @ 75-85°; core broken 5-15cm, fractures parallel to foliation, coated with sericite & locally graphite.							
		(3.0 - 6.5) Limonitic fractures.							
		(7.1 - 7.5) Mafic dyke; light grey, fine-grained, massive, moderately soft, chloritised, 3% pyrite as 1-2mm wispy stringers.							
		(7.8 - 8.1) white kaolin-coated fractures @ 0°.							
		(8.2 - 9.0) wispy pyrite stringers, discontinuous, 1-2mm; 1/2-1mm quartz stringers.							
		(13.8 - 15.8) broken core, 0.8m ground core.							
		(15.8 - 18.1) dark grey, graphitic, weakly banded.							
		(17.1) 5mm quartz-pyrite stringer @ 30°.							
		(19.4 - 21.9) broken core, 0.5m ground core.							
21.9	23.8	FAULT ZONE							
		Light grey to black, coarse-grained; quartzite breccia - 80% subrounded, 2-10mm subrounded quartzite fragments in quartz-sericite-graphite matrix; crumbly graphitic gouge, irreg. graphitic slickensides @ 80°; 80cm ground core.							
23.8	28.5	CHLORITIC BIOTITIC QUARTZITE (UNIT 2)							
		Light to medium grey, grey-brown; fine- to medium-grained, moderately laminated 2-5mm; 80% quartz, 10% biotite, 10% chlorite; foliation @ 65-75°.	71622	28.0	28.5	0.5	0.001	<0.02	
28.5	29.1	QUARTZ VEIN (Hanging Wall Vein)							
		White, dark grey, medium-grained, massive to banded; 30% dark grey pyritic wallrock bands & grey quartz; 3% pyrite as 1-3mm subhedral blebs & grains, concentrated in dark grey chloritic-graphitic wallrock, less than 1/2X light brown sphalerite; banding @ 80°; upper contact sharp @ 80°, lower irreg. @ 75°.	71623	28.5	29.1	0.6	0.228	0.87	

METRES		DESCRIPTION	CORE SAMPLES							AVERAGES				
FROM	TO		NUMBER	FROM (m)	TO (m)	WIDTH (m)	Au (OPT)	Ag (OPT)						
29.1	40.8	<p>BIOTITIC CHLORITIC QUARTZITE (UNIT 2)</p> <p>Medium grey, medium grey-brown, fine- to medium-grained, moderately laminated 1-7mm; 80% quartz, 15% chlorite, 5% biotite; occasional irreg. 1-3cm quartz stringers & indistinct blebs & 1-3mm white quartz stringers @ 0-20°; foliation @ 70-80°.</p> <p>(33.3) 1-3cm quartz stringer @ 30°; chlorite, fuchsite(?) & clay-coated margins, pyritic vein.</p> <p>(35.9) 1-1.5cm clay, fuchsite & pyrite stringer @ 25°.</p> <p>(38.3 - 39.0) disseminated pyrite & quartz stringers 1-7mm @ 10-20°; quartz stringers are vuggy, medium-grained.</p> <p>(39.6 - 40.8) medium to dark grey, graphitic, well laminated locally, 3% pyrite.</p>	71624	29.1	29.6	0.5	0.003	0.03						
40.8	51.6	<p>CALCAREOUS INTERMEDIATE TUFF</p> <p>Dark green, brown, grey, light grey; medium-grained, finely laminated 1-5mm, banded ½-2cm; comprised of quartz, feldspar, chlorite, amphibole, biotite, calcite grains; locally weakly calcareous matrix, 5% ½-1cm grey calcite bands; occasional irreg. white quartz bands subparallel foliation; foliation: @50° at 46.0m, @60° at 49.7m, @ 65° at 52.1m.</p> <p>(40.8) medium brown, 70% biotite & irreg. shreds calcite 20%, 10% quartz.</p> <p>(41.5 - 46.3) laminated & foliated @ 0-30°, open cm-scale folds, locally contorted.</p> <p>(45.9 - 46.3) broken core.</p> <p>(47.3) 20cm broken core.</p> <p>(50.4) 20cm broken core.</p>												
51.6	53.9	<p>CHLORITIC QUARTZITE (UNIT 2)</p> <p>Light grey, green-grey; fine-grained, finely to moderately laminated; quartz, chlorite, sericite, graphite, biotite; graphitic foliation planes. foliation @ 55-60°.</p>	71625	53.4	53.9	0.5	0.001	0.04						
53.9	54.3	<p>QUARTZ VEIN (Main Vein)</p> <p>White, grey, yellow; medium-grained; banded with 7% pyrite concentrated in black 1-3mm graphite-chlorite bands; foliation/banding @ 75°. Vuggy fracture coated with pyrite octahedra & white 1-2mm chabazite(?) blebs, @ 15° to core axis.</p>	71626	53.9	54.3	0.4	0.025	0.08						
54.3	61.3	<p>CHLORITIC QUARTZITE (UNIT 2)</p> <p>Medium grey, fine-grained, weakly to moderately foliated @ 70-85°, finely laminated, graphitic in part.</p> <p>(57.4 - 58.0) very broken core, pyritic, graphitic quartzite with 10% ½-1cm quartz stringers.</p>	71627 71628 71629 71630 71631	54.3 55.0 55.2 56.9 57.4	55.0 55.2 55.7 57.4 58.0	0.7 0.2 0.5 0.5 0.6	0.030 0.013 0.001 0.001 0.004	0.11 0.15 0.02 0.02 0.09						

APPENDIX II

ASSAY REPORTS



Bondar Clegg Inchcape Testing Services

Certificate of Analysis

CLIENT: OLIVER GOLD CORP.
REPORT: V94-01491.4 (COMPLETE)

PROJECT: NONE GIVEN2
DATE PRINTED: 24-JAN-95 PAGE 1

SAMPLE NUMBER	ELEMENT UNITS	Wt-150 GM	WT+150 g	Au-150 OPT	Au+150 OPT	Au Tot OPT
R2 50550		IS	IS	IS	IS	IS
R2 50575		227.9	23.45	1.938	1.91	1.935
R2 66702		193.2	19.69	0.477	0.50	0.479
R2 66738		240.1	37.19	0.262	1.14	0.380
R2 66779		236.4	37.43	0.522	0.18	0.475
R2 66844		240.0	38.30	0.196	0.21	0.197
R2 66855		248.1	27.05	0.494	0.29	0.474
R2 66886		214.3	26.70	0.004	0.01	0.004
R2 66950		252.5	34.41	5.785	31.14	8.827
R2 71605		232.1	31.42	0.113	0.14	0.116
R2 71606		228.0	26.77	0.031	0.14	0.043



Bondar Clegg Inchcape Testing Services

Certificate of Analysis

CLIENT: OLIVER GOLD CORP.
REPORT: V94-01305.4 (COMPLETE)

PROJECT: FAIRVIEW
DATE PRINTED: 24-JAN-95 PAGE 1

SAMPLE NUMBER	ELEMENT UNITS	Au OPT	Au GMT	Ag OPT	Ag GMT
D2 50549		0.006	0.22	0.03	1.1
D2 50550		2.282&	78.24&	3.71	127.2
D2 50551		0.012	0.41	0.03	1.0
D2 50552		0.002	0.07	<0.02	<0.7
D2 50553		0.005	0.19	0.05	1.7
D2 50554		0.050	1.71	0.08	2.7
D2 50555		0.003	0.10	<0.02	<0.7
D2 50556		0.001	0.03	0.03	1.0
D2 50557		0.103	3.53	0.79	27.1
D2 50558		0.069	2.37	0.21	7.2
D2 50559		0.229	7.85	2.39	81.9
D2 50560		0.006	0.19	0.07	2.5
D2 50561		0.002	0.06	<0.02	<0.7
D2 50562		0.080	2.74	0.62	21.3
D2 50563		0.008	0.27	0.10	3.6
D2 50564		<0.001	<0.03	<0.02	<0.7
D2 50565		0.005	0.16	0.08	2.6
D2 50566		0.004	0.13	0.03	0.9
D2 50567		0.003	0.10	0.02	0.9
D2 50568		0.027	0.93	0.05	1.6
D2 50569		0.146	5.01	0.30	10.2
D2 50570		<0.001	<0.03	0.03	0.9
D2 50571		0.132	4.52	0.77	26.4
D2 50572		<0.001	<0.03	<0.02	<0.7
D2 50573		0.002	0.08	0.11	3.8
D2 50574		0.043	1.48	0.80	27.6
D2 50575		2.038&	69.87&	8.85	303.4
D2 50576		0.006	0.21	0.03	1.0
D2 50577		0.003	0.10	0.03	0.9
D2 50578		0.085	2.91	0.40	13.8
D2 50579		0.039	1.35	0.30	10.3
D2 50580		0.013	0.45	0.25	8.7
D2 50581		0.002	0.06	<0.02	<0.7
D2 50582		0.007	0.23	0.04	1.5
D2 50583		0.007	0.24	0.08	2.8
D2 50584		0.204	6.99	1.39	47.7
D2 50585		0.117	4.01	0.91	31.2
D2 50586		0.018	0.62	0.34	11.7
D2 50587		0.001	0.03	<0.02	<0.7



Bondar Clegg Inchcape Testing Services

Certificate of Analysis

CLIENT: OLIVER GOLD CORP.
REPORT: V94-01348.4 (COMPLETE)

PROJECT: NONE GIVEN1
DATE PRINTED: 7-DEC-94 PAGE 1

SAMPLE NUMBER	ELEMENT UNITS	Au GMT	Au OPT	Ag GMT	Ag OPT	SAMPLE NUMBER	ELEMENT UNITS	Au GMT	Au OPT	Ag GMT	Ag OPT
D2 V50588		<0.03	<0.001	<0.7	<0.02	D2 V50628		<0.03	<0.001	<0.7	<0.02
D2 V50589		0.20	0.006	2.0	0.06	D2 V50629		<0.03	<0.001	<0.7	<0.02
D2 V50590		0.10	0.003	1.3	0.04	D2 V50630		<0.03	<0.001	<0.7	<0.02
D2 V50591		0.69	0.020	4.4	0.13	D2 V50631		0.07	0.002	1.6	0.05
D2 V50592		0.41	0.012	5.3	0.16	D2 V50632		0.56	0.016	8.3	0.24
D2 V50593		0.08	0.002	2.0	0.06	D2 V50633		0.06	0.002	1.7	0.05
D2 V50594		0.09	0.003	2.5	0.07	D2 V50634		0.09	0.003	2.3	0.07
D2 V50595		0.07	0.002	0.9	0.02	D2 V50635		<0.03	<0.001	0.8	0.02
D2 V50596		0.07	0.002	<0.7	<0.02						
D2 V50597		1.85	0.054	3.8	0.11						
D2 V50598		0.07	0.002	0.8	0.02						
D2 V50599		<0.03	<0.001	<0.7	<0.02						
D2 V50600		0.06	0.002	1.0	0.03						
D2 V50601		0.11	0.003	0.9	0.03						
D2 V50602		0.05	0.002	0.8	0.02						
D2 V50603		<0.03	<0.001	1.2	0.04						
D2 V50604		<0.03	<0.001	<0.7	<0.02						
D2 V50605		0.10	0.003	1.0	0.03						
D2 V50606		0.03	0.001	1.0	0.03						
D2 V50607		0.17	0.005	3.7	0.11						
D2 V50608		0.08	0.002	1.6	0.05						
D2 V50609		0.11	0.003	2.2	0.06						
D2 V50610		<0.03	<0.001	1.0	0.03						
D2 V50611		<0.03	<0.001	<0.7	<0.02						
D2 V50612		<0.03	<0.001	<0.7	<0.02						
D2 V50613		<0.03	<0.001	<0.7	<0.02						
D2 V50614		0.33	0.010	2.7	0.08						
D2 V50615		0.18	0.005	0.9	0.03						
D2 V50616		<0.03	<0.001	0.8	0.02						
D2 V50617		<0.03	<0.001	<0.7	<0.02						
D2 V50618		<0.03	<0.001	<0.7	<0.02						
D2 V50619		<0.03	<0.001	<0.7	<0.02						
D2 V50620		<0.03	<0.001	<0.7	<0.02						
D2 V50621		0.33	0.010	3.0	0.09						
D2 V50622		0.04	0.001	0.9	0.03						
D2 V50623		0.14	0.004	1.1	0.03						
D2 V50624		2.33	0.068	38.1	1.11						
D2 V50625		0.06	0.002	1.4	0.04						
D2 V50626		<0.03	<0.001	1.4	0.04						
D2 V50627		0.07	0.002	1.0	0.03						



Bondar Clegg Inchcape Testing Services

Certificate of Analysis

REPORT: V94-01351.4 (COMPLETE)

DATE PRINTED: 2-DEC-94

PROJECT: NONE GIVEN1

PAGE 1


SAMPLE NUMBER	ELEMENT UNITS	Au		Ag	
		GMT	OPT	GMT	OPT
D2 V50636		<0.03	<0.001	<0.7	<0.02
D2 V50637		0.12	0.004	1.5	0.04
D2 V50638		0.13	0.004	1.5	0.04
D2 V50639		0.15	0.004	1.4	0.04
D2 V50640		0.06	0.002	1.3	0.04
D2 V50641		0.10	0.003	<0.7	<0.02
D2 V50642		0.15	0.004	1.7	0.05
D2 V50643		0.14	0.004	2.6	0.07
D2 V50644		0.15	0.004	2.0	0.06
D2 V50645		<0.03	<0.001	<0.7	<0.02
D2 V50646		0.15	0.004	1.5	0.04
D2 V50647		3.51	0.102	24.2	0.71
D2 V50648		0.28	0.008	0.9	0.03
D2 V50649		2.23	0.065	1.4	0.04
D2 V50650		0.09	0.003	<0.7	<0.02
D2 V50651		0.14	0.004	1.2	0.03
D2 V50652		9.98	0.291	25.6	0.75
D2 V50653		0.55	0.016	3.7	0.11
D2 V50654		3.27	0.095	12.3	0.36
D2 V50655		0.38	0.011	3.6	0.10
D2 V50656		0.06	0.002	0.7	0.02
D2 V50657		0.94	0.027	2.5	0.07
D2 V50658		<0.03	<0.001	1.1	0.03
D2 V50659		<0.03	<0.001	<0.7	<0.02
D2 V50660		0.05	0.001	2.5	0.07
D2 V50661		0.10	0.003	1.7	0.05
D2 V50662		<0.03	<0.001	<0.7	<0.02
D2 V50663		<0.03	<0.001	<0.7	<0.02
D2 V50664		0.72	0.021	18.5	0.54
D2 V50665		0.15	0.004	3.2	0.09
D2 V50666		0.15	0.004	4.3	0.12
D2 V50667		0.11	0.003	1.8	0.05
D2 V50668		0.18	0.005	1.2	0.03
D2 V50669		0.04	0.001	0.8	0.02
D2 V50670		1.43	0.042	5.0	0.14

reassayed see Rept. V94-01351.5 Feb. 1

Bondar-Clegg & Company Ltd.

130 Pemberton Avenue, North Vancouver, B.C., V7P 2R5, Canada

Tel: (604) 985-0681, Fax: (604) 985-1071



Registered Assayer, Province of British Columbia



Bondar Clegg Inchcape Testing Services

Certificate of Analysis

CLIENT: OLIVER GOLD CORP.
REPORT: V94-01351.6 (COMPLETE)

PROJECT: NONE GIVEN1
DATE PRINTED: 1-FEB-95 PAGE 1

SAMPLE NUMBER	ELEMENT UNITS	Wt-150 GM	WT+150 g	Au-150 OPT	Au+150 OPT	Au Tot OPT	Au OPT
DW V50651		213.6	1.50	0.312	6.126	0.353	0.353
DW V50653		306.6	1.70	0.017	<0.001	0.017	0.017



Bondar Clegg Inchcape Testing Services

Certificate of Analysis

CLIENT: OLIVER GOLD CORP.
REPORT: V94-01351.5 (COMPLETE)

PROJECT: NONE GIVEN1
DATE PRINTED: 1-FEB-95 PAGE 1

SAMPLE NUMBER	ELEMENT UNITS	Au		Ag	
		GMT	OPT	GMT	OPT
D2 V50652		0.09	0.002	<0.7	<0.02

CLIENT: OLIVER GOLD CORP.
REPORT: V95-00107.4 (COMPLETE)

PROJECT: NONE GIVEN
DATE PRINTED: 20-FEB-95 PAGE 1

SAMPLE NUMBER	ELEMENT UNITS	WT-150 GM	WT+150 g	Au-150 OPT	Au+150 OPT	Au Tot OPT	Au OPT	Ag OPT
R2 V50651Q		214.9	10.10	0.758	4.26	0.915		0.93
R2 V50652Q							0.003	<0.02



Bondar Clegg Inchcape Testing Services

Certificate of Analysis

REPORT: V94-01358.4 (COMPLETE)

DATE PRINTED: 5-DEC-94

PROJECT: NONE GIVEN1

PAGE 1

SAMPLE NUMBER	ELEMENT UNITS	Au OPT	Au GMT	Ag OPT	Ag GMT
D2 50671		0.037	1.28	0.46	15.7
D2 50672		0.002	0.09	0.05	1.8
D2 50673		0.003	0.10	<0.02	<0.7
D2 50674		0.011	0.37	0.05	1.7
D2 50675		0.002	0.05	<0.02	<0.7
D2 50676		0.023	0.79	0.38	13.0
D2 50677		<0.001	<0.03	0.02	0.7
D2 50678		0.002	0.09	0.08	2.6
D2 50679		0.003	0.09	0.06	2.2
D2 50680		0.010	0.34	0.21	7.0
D2 50681		0.001	0.04	0.04	1.4
D2 50682		0.043	1.48	0.07	2.3
D2 50683		<0.001	<0.03	<0.02	<0.7
D2 50684		<0.001	<0.03	<0.02	<0.7
D2 50685		<0.001	<0.03	<0.02	<0.7
D2 50686		<0.001	<0.03	<0.02	<0.7
D2 50687		<0.001	<0.03	0.03	0.9
D2 50688		<0.001	<0.03	0.02	0.7
D2 50689		<0.001	<0.03	0.03	1.1
D2 50690		0.001	0.04	0.02	0.9
D2 50691		0.006	0.20	0.14	4.8
D2 50692		<0.001	<0.03	0.03	1.0
D2 50693		0.014	0.47	0.06	2.1
D2 50694		0.001	0.03	0.03	1.0



Bondar Clegg Inchcape Testing Services

Certificate of Analysis

CLIENT: OLIVER GOLD CORP.
REPORT: V94-01361.4 (COMPLETE)

PROJECT: NONE GIVEN1
DATE PRINTED: 30-JAN-95 PAGE 1

SAMPLE NUMBER	ELEMENT UNITS	Au GMT	Au OPT	Ag GMT	Ag OPT
D2 50695		<0.03	<0.001	<0.7	<0.02
D2 50696		0.15	0.004	0.8	0.02
D2 50697		<0.03	<0.001	<0.7	<0.02
D2 50698		<0.03	<0.001	<0.7	<0.02
D2 50699		<0.03	<0.001	<0.7	<0.02
D2 50700		<0.03	<0.001	<0.7	<0.02
D2 66701		0.09	0.003	1.3	0.04
D2 66702		18.07	0.527	276.3	8.06
D2 66703		1.10	0.032	9.9	0.29
D2 66704		<0.03	<0.001	0.8	0.02
D2 66705		<0.03	<0.001	<0.7	<0.02
D2 66706		1.78	0.052	27.4	0.80
D2 66707		0.04	0.001	1.0	0.03
D2 66708		<0.03	<0.001	<0.7	<0.02
D2 66709		<0.03	<0.001	<0.7	<0.02
D2 66710		3.26	0.095	33.9	0.99
D2 66711		0.77	0.022	5.5	0.16
D2 66712		0.79	0.023	4.8	0.14
D2 66713		<0.03	<0.001	0.8	0.02
D2 66714		0.11	0.003	4.0	0.12
D2 66715		0.22	0.007	6.2	0.18
D2 66716		<0.03	<0.001	<0.7	<0.02
D2 66717		<0.03	<0.001	<0.7	<0.02
D2 66718		0.13	0.004	<0.7	<0.02
D2 66719		0.11	0.003	<0.7	<0.02
D2 66720		0.10	0.003	<0.7	<0.02
D2 66721		0.14	0.004	0.8	0.02
D2 66722		0.12	0.003	<0.7	<0.02



Bondar Clegg Inchcape Testing Services

Certificate of Analysis

CLIENT: OLIVER GOLD CORP.
REPORT: V94-01412.4 (COMPLETE)

PROJECT: NONE GIVEN1
DATE PRINTED: 16-DEC-94 PAGE 1

SAMPLE NUMBER	ELEMENT UNITS	Au GMT	Au OPT	Ag GMT	Ag OPT	SAMPLE NUMBER	ELEMENT UNITS	Au GMT	Au OPT	Ag GMT	Ag OPT
D2 V66723		<0.03	<0.001	<0.7	<0.02	D2 V66763		<0.03	<0.001	<0.7	<0.02
D2 V66724		<0.03	<0.001	<0.7	<0.02	D2 V66764		<0.03	<0.001	<0.7	<0.02
D2 V66725		<0.03	<0.001	<0.7	<0.02	D2 V66765		<0.03	<0.001	0.7	0.02
D2 V66726		<0.03	<0.001	<0.7	<0.02	D2 V66766		<0.03	<0.001	<0.7	<0.02
D2 V66727		0.10	0.003	0.7	0.02	D2 V66767		0.66	0.019	6.5	0.19
D2 V66728		0.34	0.010	1.0	0.03	D2 V66768		1.47	0.043	35.3	1.03
D2 V66729		0.32	0.009	3.8	0.11	D2 V66769		0.82	0.024	10.6	0.31
D2 V66730		1.84	0.054	3.2	0.09	D2 V66770		2.67	0.078	28.1	0.82
D2 V66731		2.02	0.059	1.6	0.05	D2 V66771		0.58	0.017	17.8	0.52
D2 V66732		0.17	0.005	<0.7	<0.02	D2 V66772		3.53	0.103	30.5	0.89
D2 V66733		0.11	0.003	<0.7	<0.02	D2 V66773		0.14	0.004	27.8	0.81
D2 V66734		0.55	0.016	7.6	0.22	D2 V66774		<0.03	<0.001	1.4	0.04
D2 V66735		0.15	0.004	1.9	0.05	D2 V66775		0.96	0.028	5.7	0.17
D2 V66736		0.25	0.007	1.3	0.04	D2 V66776		<0.03	<0.001	<0.7	<0.02
D2 V66737		2.50	0.073	4.1	0.12	D2 V66777		<0.03	<0.001	1.0	0.03
D2 V66738		20.67	0.603	18.2	0.53	D2 V66778		<0.03	<0.001	<0.7	<0.02
D2 V66739		0.27	0.008	2.7	0.08	D2 V66779		17.69	0.516	226.3	6.60
D2 V66740		<0.03	<0.001	1.0	0.03	D2 V66780		0.45	0.013	1.7	0.05
D2 V66741		0.24	0.007	4.1	0.12	D2 V66781		3.09	0.090	11.1	0.32
D2 V66742		<0.03	<0.001	1.0	0.03	D2 V66782		0.07	0.002	0.9	0.02
D2 V66743		<0.03	<0.001	1.0	0.03	D2 V66783		<0.03	<0.001	0.8	0.02
D2 V66744		<0.03	<0.001	<0.7	<0.02	D2 V66784		0.34	0.010	3.7	0.11
D2 V66745		<0.03	<0.001	2.1	0.06	D2 V66785		3.15	0.092	16.1	0.47
D2 V66746		0.04	0.001	3.1	0.09	D2 V66786		0.76	0.022	1.7	0.05
D2 V66747		0.32	0.009	3.0	0.09	D2 V66787		2.22	0.065	3.1	0.09
D2 V66748		0.25	0.007	4.0	0.12	D2 V66788		<0.03	<0.001	<0.7	<0.02
D2 V66749		<0.03	<0.001	0.8	0.02	D2 V66789		0.45	0.013	4.1	0.12
D2 V66750		0.05	0.001	0.7	0.02	D2 V66790		7.13	0.208	28.1	0.82
D2 V66751		0.03	0.001	1.0	0.03	D2 V66791		8.74	0.255	59.3	1.73
D2 V66752		0.03	0.001	0.7	0.02	D2 V66792		3.15	0.092	40.5	1.18
D2 V66753		0.03	0.001	1.0	0.03	D2 V66793		0.27	0.008	8.3	0.24
D2 V66754		0.31	0.009	4.5	0.13	D2 V66794		0.14	0.004	2.2	0.06
D2 V66755		<0.03	<0.001	<0.7	<0.02	D2 V66795		0.47	0.014	4.4	0.13
D2 V66756		0.14	0.004	2.1	0.06	D2 V66796		0.78	0.023	7.1	0.21
D2 V66757		0.23	0.007	4.6	0.13	D2 V66797		1.79	0.052	32.3	0.94
D2 V66758		0.31	0.009	2.7	0.08	D2 V66798		0.28	0.008	3.4	0.10
D2 V66759		0.14	0.004	2.7	0.08						
D2 V66760		<0.03	<0.001	0.7	0.02						
D2 V66761		0.14	0.004	1.0	0.03						
D2 V66762		<0.03	<0.001	1.0	0.03						



Bondar Clegg Inchcape Testing Services

Certificate of Analysis

CLIENT: OLIVER GOLD CORP.
REPORT: V94-01427.4 (COMPLETE)

PROJECT: NONE GIVEN1
DATE PRINTED: 23-DEC-94 PAGE 1

SAMPLE NUMBER	ELEMENT UNITS	Au GMT	Au OPT	Ag GMT	Ag OPT	SAMPLE NUMBER	ELEMENT UNITS	Au GMT	Au OPT	Ag GMT	Ag OPT
D2 V66799		<0.03	<0.001	<0.7	<0.02	D2 V66839		0.36	0.010	1.0	0.03
D2 V66800		0.05	0.001	<0.7	<0.02	D2 V66840		0.04	0.001	<0.7	<0.02
D2 V66801		<0.03	<0.001	<0.7	<0.02	D2 V66841		0.72	0.021	54.2	1.58
D2 V66802		0.30	0.009	2.9	0.09	D2 V66842		0.16	0.005	2.7	0.08
D2 V66803		0.19	0.005	1.6	0.05	D2 V66843		0.99	0.029	44.6	1.30
D2 V66804		0.12	0.004	3.7	0.11	D2 V66844		5.79	0.169	14.2	0.41
D2 V66805		0.04	0.001	1.1	0.03	D2 V66845		0.15	0.004	2.2	0.06
D2 V66806		<0.03	<0.001	<0.7	<0.02	D2 V66846		0.09	0.003	1.6	0.05
D2 V66807		0.41	0.012	16.2	0.47	D2 V66847		<0.03	<0.001	<0.7	<0.02
D2 V66808		0.03	0.001	0.7	0.02	D2 V66848		0.04	0.001	<0.7	<0.02
D2 V66809		<0.03	<0.001	<0.7	<0.02	D2 V66849		<0.03	<0.001	<0.7	<0.02
D2 V66810		0.07	0.002	1.6	0.05	D2 V66850		5.58	0.163	2.8	0.08
D2 V66811		<0.03	<0.001	<0.7	<0.02	D2 V66851		0.15	0.004	<0.7	<0.02
D2 V66812		<0.03	<0.001	0.9	0.02	D2 V66852		0.72	0.021	1.5	0.04
D2 V66813		0.12	0.003	2.2	0.06	D2 V66853		<0.03	<0.001	<0.7	<0.02
D2 V66814		0.30	0.009	9.1	0.27	D2 V66854		5.14	0.150	54.5	1.59
D2 V66815		<0.03	<0.001	0.9	0.03	D2 V66855		17.66	0.515	54.5	1.59
D2 V66816		0.07	0.002	1.4	0.04	D2 V66856		6.82	0.199	84.3	2.46
D2 V66817		<0.03	<0.001	<0.7	<0.02	D2 V66857		0.11	0.003	1.0	0.03
D2 V66818		<0.03	<0.001	<0.7	<0.02	D2 V66858		0.08	0.002	<0.7	<0.02
D2 V66819		0.28	0.008	2.7	0.08	D2 V66859		2.09	0.061	7.1	0.21
D2 V66820		1.47	0.043	9.6	0.28	D2 V66860		0.85	0.025	23.2	0.68
D2 V66821		0.31	0.009	2.7	0.08	D2 V66861		0.48	0.014	3.3	0.10
D2 V66822		<0.03	<0.001	<0.7	<0.02	D2 V66862		1.00	0.029	5.5	0.16
D2 V66823		<0.03	<0.001	0.7	0.02	D2 V66863		0.56	0.016	5.7	0.17
D2 V66824		0.21	0.006	2.7	0.08	D2 V66864		0.11	0.003	1.1	0.03
D2 V66825		<0.03	<0.001	<0.7	<0.02	D2 V66865		<0.03	<0.001	<0.7	<0.02
D2 V66826		<0.03	<0.001	<0.7	<0.02	D2 V66866		3.41	0.100	12.7	0.37
D2 V66827		1.89	0.055	14.7	0.43	D2 V66867		0.11	0.003	0.9	0.02
D2 V66828		1.99	0.058	37.0	1.08	D2 V66868		0.87	0.025	7.4	0.21
D2 V66829		1.17	0.034	22.3	0.65	D2 V66869		0.39	0.011	2.7	0.08
D2 V66830		0.24	0.007	1.3	0.04	D2 V66870		0.28	0.008	0.9	0.03
D2 V66831		0.07	0.002	2.4	0.07	D2 V66871		0.05	0.001	<0.7	<0.02
D2 V66832		0.03	0.001	<0.7	<0.02	D2 V66872		0.27	0.008	<0.7	<0.02
D2 V66833		<0.03	<0.001	<0.7	<0.02	D2 V66873		2.76	0.080	2.8	0.08
D2 V66834		<0.03	<0.001	<0.7	<0.02	D2 V66874		0.41	0.012	4.0	0.12
D2 V66835		0.17	0.005	3.1	0.09	D2 V66875		0.41	0.012	3.3	0.10
D2 V66836		2.54	0.074	18.5	0.54	D2 V66876		<0.03	<0.001	<0.7	<0.02
D2 V66837		0.40	0.012	0.9	0.02	D2 V66877		0.22	0.006	20.4	0.59
D2 V66838		0.24	0.007	1.0	0.03						



Bondar Clegg Inchcape Testing Services

Certificate of Analysis

CLIENT: OLIVER GOLD CORP.
REPORT: V94-01487.4 (COMPLETE)

PROJECT: NONE GIVEN2
DATE PRINTED: 9-JAN-95 PAGE 1

SAMPLE NUMBER	ELEMENT UNITS	Au GMT	Au OPT	Ag GMT	Ag OPT	SAMPLE NUMBER	ELEMENT UNITS	Au GMT	Au OPT	Ag GMT	Ag OPT
D2 V66878		0.18	0.005	0.9	0.03	D2 V66918		4.70	0.137	66.5	1.94
D2 V66879		0.87	0.025	2.0	0.06	D2 V66919		11.59	0.338	28.1	0.82
D2 V66880		3.58	0.104	1.8	0.05	D2 V66920		1.06	0.031	4.8	0.14
D2 V66881		0.92	0.027	<0.7	<0.02	D2 V66921		0.31	0.009	2.1	0.06
D2 V66882		0.04	0.001	1.0	0.03	D2 V66922		3.33	0.097	55.2	1.61
D2 V66883		0.27	0.008	4.1	0.12	D2 V66923		3.26	0.095	72.0	2.10
D2 V66884		0.31	0.009	3.4	0.10	D2 V66924		0.48	0.014	6.9	0.20
D2 V66885		0.04	0.001	<0.7	<0.02	D2 V66925		0.10	0.003	1.0	0.03
D2 V66886		0.14	0.004	1.5	0.04	D2 V66926		<0.03	<0.001	0.7	0.02
D2 V66887		2.45	0.071	8.0	0.23	D2 V66927		0.45	0.013	7.2	0.21
D2 V66888		1.03	0.030	2.7	0.08	D2 V66928		1.13	0.033	17.1	0.50
D2 V66889		21.70	0.633	175.5	5.12	D2 V66929		2.13	0.062	26.1	0.76
D2 V66890		0.69	0.020	7.2	0.21	D2 V66930		1.34	0.039	9.1	0.27
D2 V66891		1.44	0.042	19.5	0.57	D2 V66931		1.55	0.045	19.1	0.56
D2 V66892		0.27	0.008	2.9	0.09	D2 V66932		1.83	0.053	5.0	0.14
D2 V66893		0.07	0.002	<0.7	<0.02	D2 V66933		1.90	0.055	20.4	0.59
D2 V66894		<0.03	<0.001	<0.7	<0.02	D2 V66934		0.41	0.012	7.3	0.21
D2 V66895		0.03	0.001	2.5	0.07	D2 V66935		0.10	0.003	0.8	0.02
D2 V66896		0.14	0.004	0.8	0.02	D2 V66936		0.48	0.014	4.8	0.14
D2 V66897		<0.03	<0.001	<0.7	<0.02	D2 V66937		0.14	0.004	1.0	0.03
D2 V66898		9.87	0.288	117.9	3.44	D2 V66938		<0.03	<0.001	1.0	0.03
D2 V66899		4.35	0.127	42.5	1.24						
D2 V66900		2.09	0.061	28.8	0.84						
D2 V66901		1.44	0.042	21.7	0.63						
D2 V66902		0.06	0.002	0.9	0.03						
D2 V66903		0.05	0.002	0.9	0.02						
D2 V66904		4.25	0.124	50.1	1.46						
D2 V66905		0.07	0.002	1.0	0.03						
D2 V66906		0.14	0.004	1.7	0.05						
D2 V66907		0.14	0.004	2.1	0.06						
D2 V66908		0.38	0.011	5.8	0.17						
D2 V66909		<0.03	<0.001	2.1	0.06						
D2 V66910		0.07	0.002	4.8	0.14						
D2 V66911		0.19	0.006	3.5	0.10						
D2 V66912		2.26	0.066	61.7	1.80						
D2 V66913		<0.03	<0.001	1.4	0.04						
D2 V66914		<0.03	<0.001	<0.7	<0.02						
D2 V66915		<0.03	<0.001	<0.7	<0.02						
D2 V66916		0.21	0.006	2.4	0.07						
D2 V66917		0.93	0.027	15.8	0.46						



Bondar Clegg Inchcape Testing Services

Certificate of Analysis

CLIENT: OLIVER GOLD CORP.
REPORT: V94-01487.5 (COMPLETE)

PROJECT: NONE GIVEN2
DATE PRINTED: 31-JAN-95 PAGE 1

SAMPLE NUMBER	ELEMENT UNITS	Wt-150 GM	WT+150 g	Au-150 OPT	Au+150 OPT	Au Tot OPT	Au GMT
DW V66887		256.6	10.23	0.078	0.040	0.077	2.64



Bondar Clegg Inchcape Testing Services

Certificate of Analysis

CLIENT: OLIVER GOLD CORP.
REPORT: V94-01488.4 (COMPLETE)

PROJECT: NONE GIVEN2
DATE PRINTED: 16-JAN-95 PAGE 1

SAMPLE NUMBER	ELEMENT UNITS	Au GMT	Au OPT	Ag GMT	Ag OPT	SAMPLE NUMBER	ELEMENT UNITS	Au GMT	Au OPT	Ag GMT	Ag OPT
D2 V66939		0.13	0.004	1.7	0.05	D2 V66979		0.09	0.002	2.8	0.08
D2 V66940		<0.03	<0.001	1.0	0.03	D2 V66980		<0.03	<0.001	<0.7	<0.02
D2 V66941		<0.03	<0.001	<0.7	<0.02	D2 V66981		0.29	0.008	4.3	0.12
D2 V66942		<0.03	<0.001	<0.7	<0.02	D2 V66982		0.15	0.004	1.9	0.05
D2 V66943		0.05	0.002	2.2	0.06	D2 V66983		0.12	0.003	<0.7	<0.02
D2 V66944		<0.03	<0.001	<0.7	<0.02	D2 V66984		1.43	0.042	7.7	0.22
D2 V66945		0.18	0.005	<0.7	<0.02	D2 V66985		87.74	2.559	121.7	3.55
D2 V66946		<0.03	<0.001	<0.7	<0.02	D2 V66986		0.38	0.011	6.4	0.19
D2 V66947		0.27	0.008	15.6	0.46	D2 V66987		<0.03	<0.001	<0.7	<0.02
D2 V66948		1.52	0.044	22.3	0.65	D2 V66988		0.10	0.003	<0.7	<0.02
D2 V66949		0.61	0.018	10.9	0.32	D2 V66989		3.53	0.103	41.8	1.22
D2 V66950		245.21	7.152	156.3	4.56	D2 V66990		0.18	0.005	2.7	0.08
D2 V66951		7.41	0.216	6.6	0.19	D2 V66991		0.14	0.004	<0.7	<0.02
D2 V66952		0.17	0.005	1.0	0.03	D2 V66992		0.04	0.001	1.4	0.04
D2 V66953		0.24	0.007	0.8	0.02	D2 V66993		0.98	0.029	1.0	0.03
D2 V66954		1.75	0.051	2.0	0.06	D2 V66994		21.12	0.616	31.9	0.93
D2 V66955		0.10	0.003	0.7	0.02	D2 V66995		0.05	0.002	<0.7	<0.02
D2 V66956		0.69	0.020	11.0	0.32	D2 V66996		0.07	0.002	2.0	0.06
D2 V66957		1.69	0.049	29.0	0.84	D2 V66997		0.10	0.003	1.5	0.04
D2 V66958		0.20	0.006	2.8	0.08	D2 V66998		<0.03	<0.001	<0.7	<0.02
D2 V66959		0.04	0.001	<0.7	<0.02	D2 V66999		0.15	0.004	1.4	0.04
D2 V66960		0.45	0.013	3.5	0.10	D2 V67000		0.06	0.002	<0.7	<0.02
D2 V66961		0.11	0.003	1.2	0.03	D2 V71601		<0.03	<0.001	<0.7	<0.02
D2 V66962		1.16	0.034	7.5	0.22	D2 V71602		0.04	0.001	1.0	0.03
D2 V66963		1.08	0.031	6.6	0.19	D2 V71603		0.21	0.006	1.4	0.04
D2 V66964		1.74	0.051	9.0	0.26	D2 V71604		2.67	0.078	20.1	0.59
D2 V66965		2.09	0.061	3.2	0.09	D2 V71605		6.71	0.196	15.7	0.46
D2 V66966		13.75	0.401	46.6	1.36	D2 V71606		2.67	0.078	10.4	0.30
D2 V66967		0.51	0.015	5.8	0.17	D2 V71607		0.25	0.007	5.6	0.16
D2 V66968		0.17	0.005	3.8	0.11	D2 V71608		1.21	0.035	28.3	0.83
D2 V66969		0.87	0.025	10.1	0.29	D2 V71609		0.10	0.003	2.0	0.06
D2 V66970		0.08	0.002	<0.7	<0.02	D2 V71610		0.07	0.002	<0.7	<0.02
D2 V66971		0.05	0.001	<0.7	<0.02	D2 V71611		0.26	0.008	1.1	0.03
D2 V66972		30.31	0.884	13.7	0.40	D2 V71612		0.31	0.009	3.1	0.09
D2 V66973		4.37	0.128	2.4	0.07	D2 V71613		0.43	0.012	3.0	0.09
D2 V66974		0.32	0.009	5.3	0.15	D2 V71614		0.30	0.009	1.7	0.05
D2 V66975		0.04	0.001	<0.7	<0.02	D2 V71615		0.60	0.018	6.9	0.20
D2 V66976		<0.03	<0.001	<0.7	<0.02	D2 V71616		3.20	0.093	20.6	0.60
D2 V66977		<0.03	<0.001	<0.7	<0.02	D2 V71617		0.06	0.002	1.3	0.04
D2 V66978		0.17	0.005	2.7	0.08	D2 V71618		0.23	0.007	1.4	0.04



Bondar Clegg Inchcape Testing Services

Certificate of Analysis

CLIENT: OLIVER GOLD CORP.
REPORT: V94-01488.4 (COMPLETE)

PROJECT: NONE GIVEN2
DATE PRINTED: 16-JAN-95 PAGE 2

SAMPLE NUMBER	ELEMENT UNITS	Au GMT	Au OPT	Ag GMT	Ag OPT	SAMPLE NUMBER	ELEMENT UNITS	Au GMT	Au OPT	Ag GMT	Ag OPT
2 V71619		0.21	0.006	1.0	0.03						
D2 V71620		<0.03	<0.001	<0.7	<0.02						
2 V71621		1.17	0.034	0.7	0.02						
2 V71622		0.04	0.001	<0.7	<0.02						
D2 V71623		7.82	0.228	29.8	0.87						
2 V71624		0.09	0.003	0.9	0.03						
D2 V71625		0.04	0.001	1.5	0.04						
D2 V71626		0.84	0.025	2.8	0.08						
2 V71627		1.01	0.030	3.7	0.11						
2 V71628		0.45	0.013	5.3	0.15						
2 V71629		<0.03	<0.001	<0.7	<0.02						
2 V71630		<0.03	<0.001	<0.7	<0.02						
D2 V71631		0.15	0.004	3.2	0.09						
D2 V71632		0.21	0.006	2.5	0.07						
2 V71633		0.36	0.010	6.9	0.20						





Bondar Clegg Inchcape Testing Services

Geochemical Lab Report

CLIENT: OLIVER GOLD CORP.
REPORT: V95-00021.0 (COMPLETE)

PROJECT: NONE GIVEN1
DATE PRINTED: 10-JAN-95 PAGE 1

SAMPLE NUMBER	ELEMENT UNITS	SG S/G
R2 50652		2.7
R2 66702		2.7
R2 66950		2.9
R2 66955		2.7

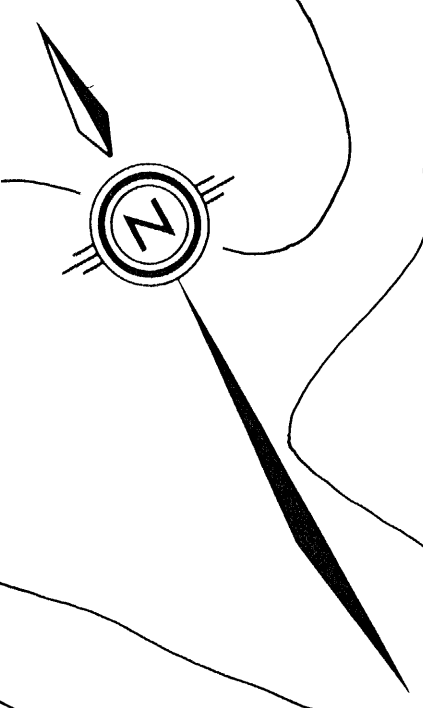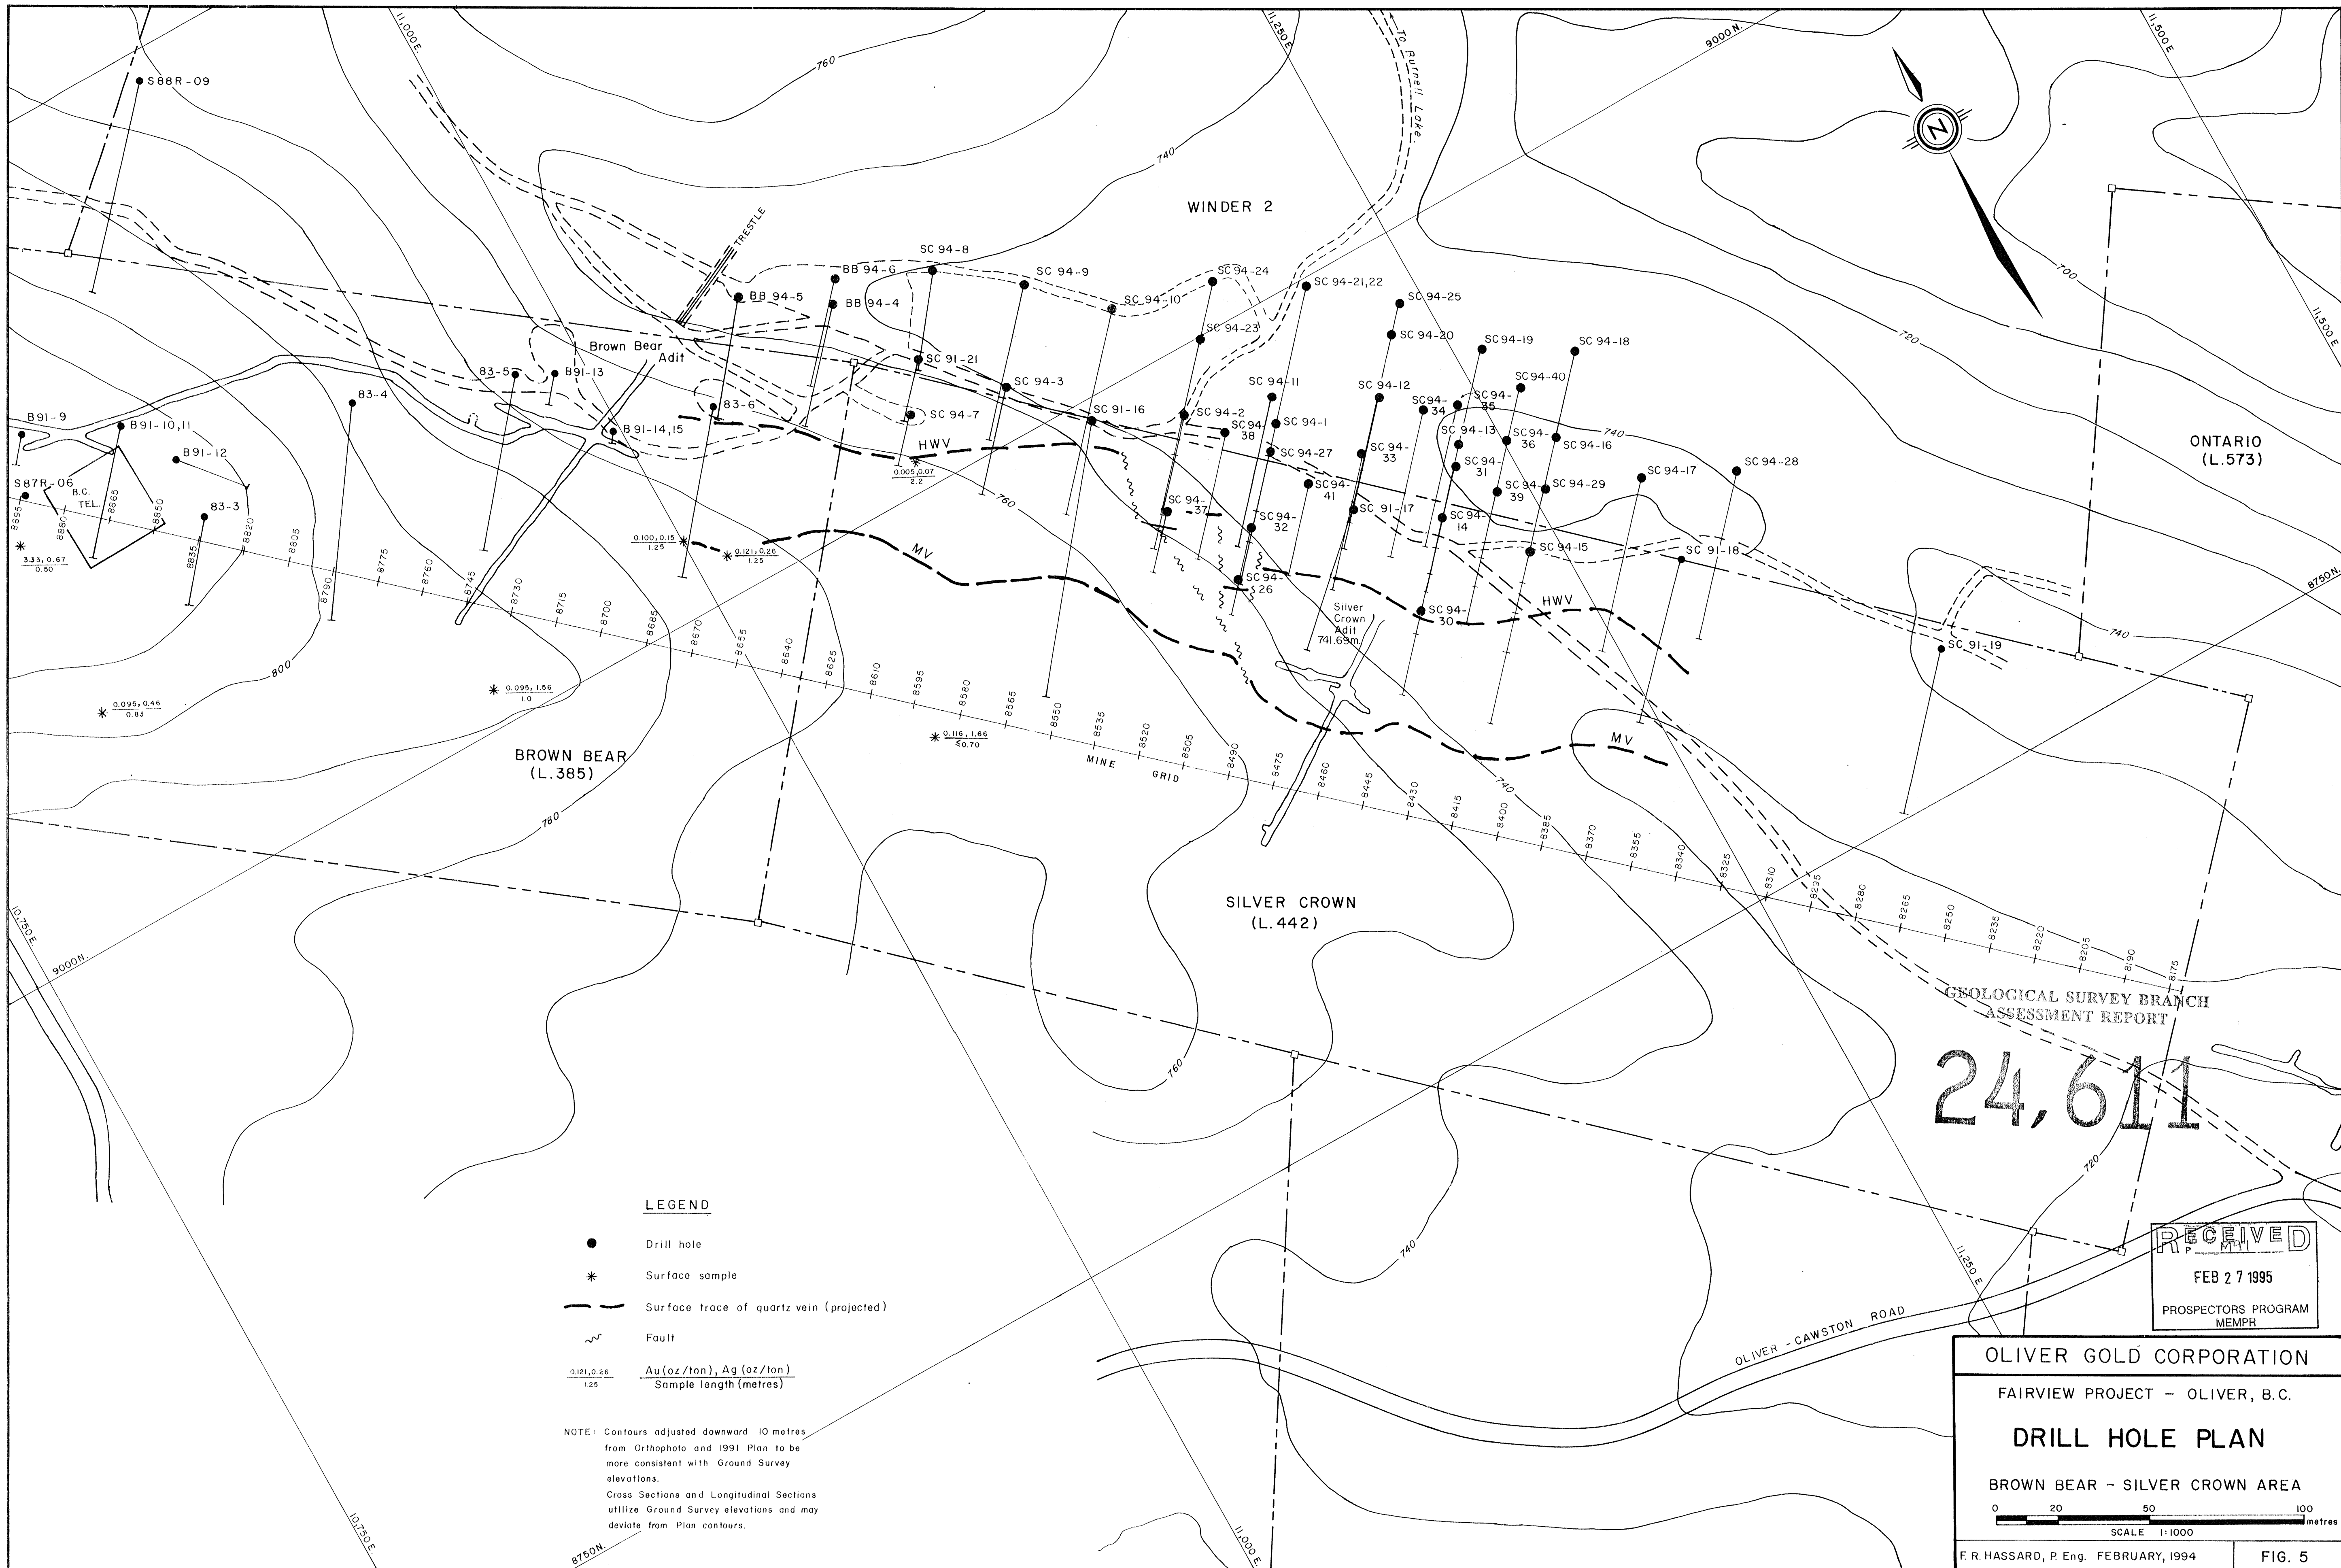

BROWN BEAR
(L. 385)

SILVER CROWN
(L. 442)

ONTARIO
(L. 573)

LEGEND

- Drill hole
- * Surface sample
- Surface trace of quartz vein (projected)
- ~ Fault
- $\frac{0.121, 0.26}{1.25}$ Au (oz/ton), Ag (oz/ton)
Sample length (metres)

NOTE: Contours adjusted downward 10 metres from Orthophoto and 1991 Plan to be more consistent with Ground Survey elevations.
Cross Sections and Longitudinal Sections utilize Ground Survey elevations and may deviate from Plan contours.

GEOLOGICAL SURVEY BRANCH
ASSESSMENT REPORT


24,611

RECEIVED
FEB 27 1995
PROSPECTORS PROGRAM
MEMBER

OLIVER GOLD CORPORATION
FAIRVIEW PROJECT - OLIVER, B.C.
DRILL HOLE PLAN
BROWN BEAR - SILVER CROWN AREA

0 20 50 100 metres
SCALE 1:1000

F. R. HASSARD, P. Eng. FEBRUARY, 1994

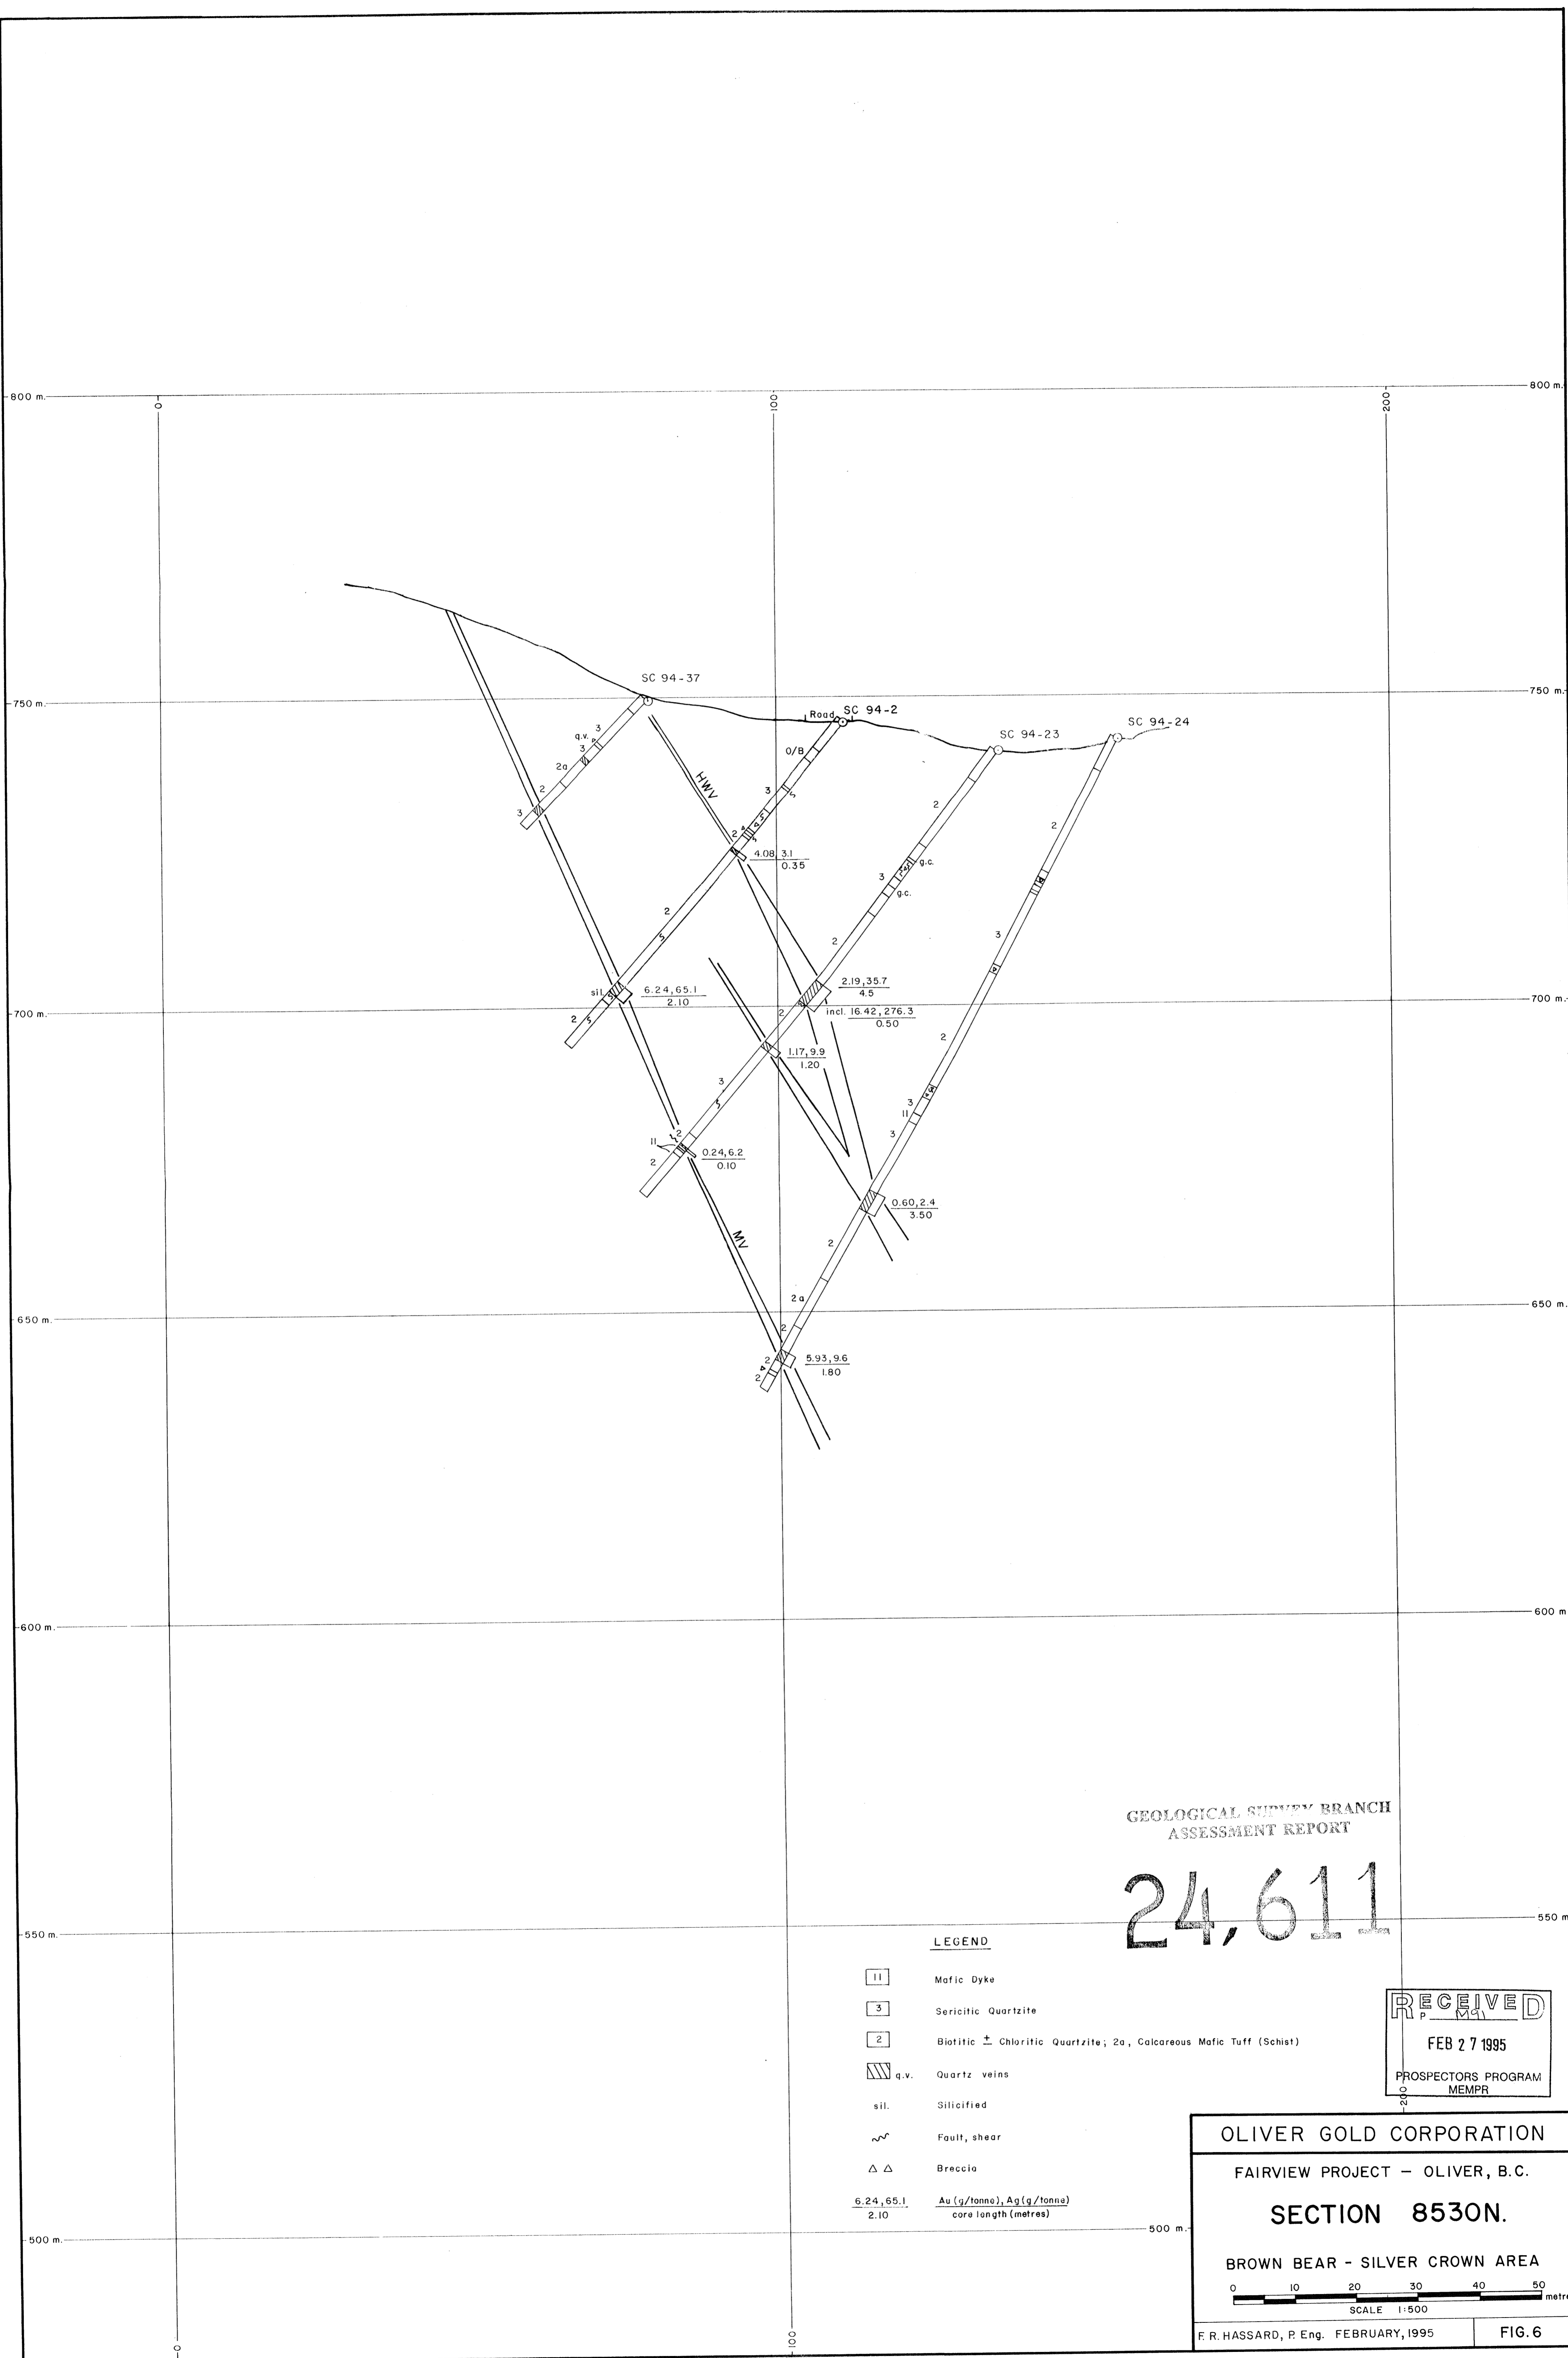

GEOLOGICAL SURVEY BRANCH
ASSESSMENT REPORT


24,611

LEGEND

- 11 Mafic Dyke
- 3 Sericitic Quartzite
- 2 Biotitic ± Chloritic Quartzite; 2a, Calcareous Mafic Tuff (Schist)
- q.v. Quartz veins
- sil. Silicified
- ~ Fault, shear
- Δ Δ Breccia
- $\frac{6.24, 65.1}{2.10}$ $\frac{\text{Au (g/tonne), Ag (g/tonne)}}{\text{core length (metres)}}$

RECEIVED
FEB 27 1995
PROSPECTORS PROGRAM
MEMPR

OLIVER GOLD CORPORATION
FAIRVIEW PROJECT - OLIVER, B.C.
SECTION 8530N.
BROWN BEAR - SILVER CROWN AREA
0 10 20 30 40 50 metres
SCALE 1:500
F. R. HASSARD, P. Eng. FEBRUARY, 1995
FIG. 6

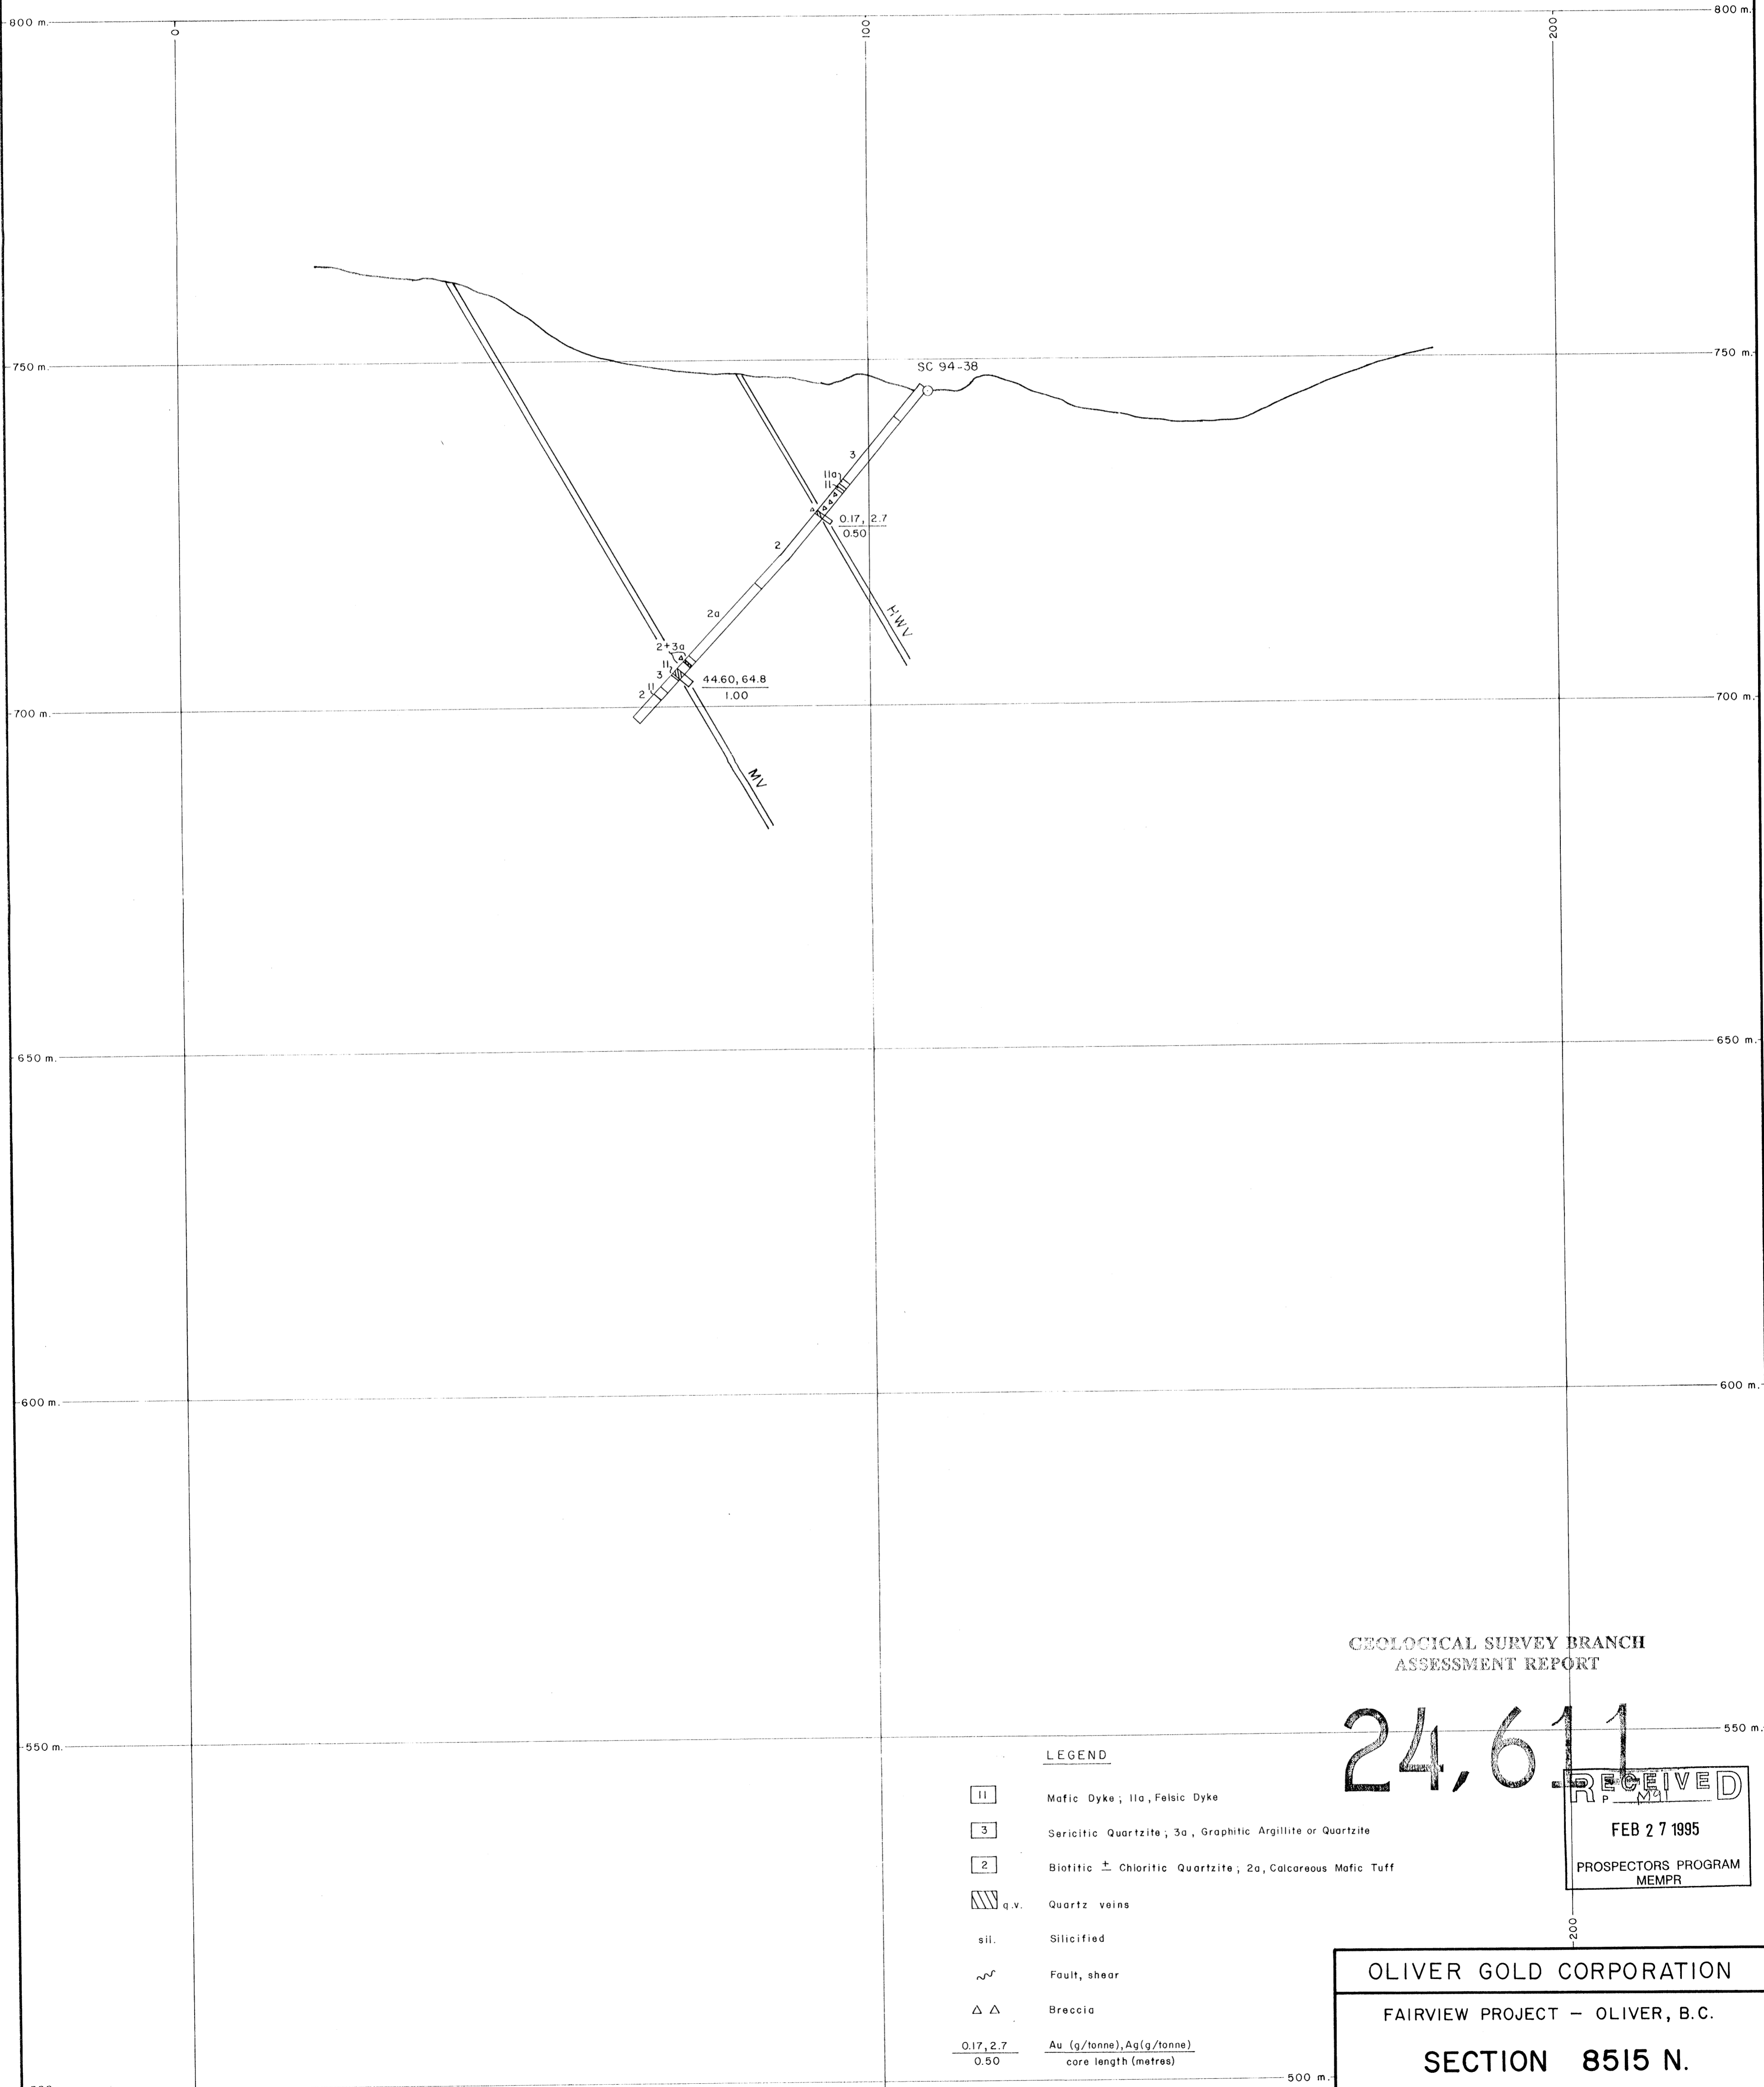

GEOLOGICAL SURVEY BRANCH
ASSESSMENT REPORT

24,611

RECEIVED
FEB 27 1995
PROSPECTORS PROGRAM
MEMPR

LEGEND


□ 11	Mafic Dyke; 11a, Felsic Dyke
□ 3	Sericitic Quartzite; 3a, Graphitic Argillite or Quartzite
□ 2	Biotitic ± Chloritic Quartzite; 2a, Calcareous Mafic Tuff
▨ q.v.	Quartz veins
sil.	Silicified
~	Fault, shear
△ △	Breccia
$\frac{0.17, 2.7}{0.50}$	$\frac{\text{Au (g/tonne), Ag (g/tonne)}}{\text{core length (metres)}}$

OLIVER GOLD CORPORATION
FAIRVIEW PROJECT - OLIVER, B.C.
SECTION 8515 N.
BROWN BEAR - SILVER CROWN AREA

0 10 20 30 40 50 metres
SCALE 1:500

F. R. HASSARD, P. Eng. FEBRUARY, 1995

FIG. 7

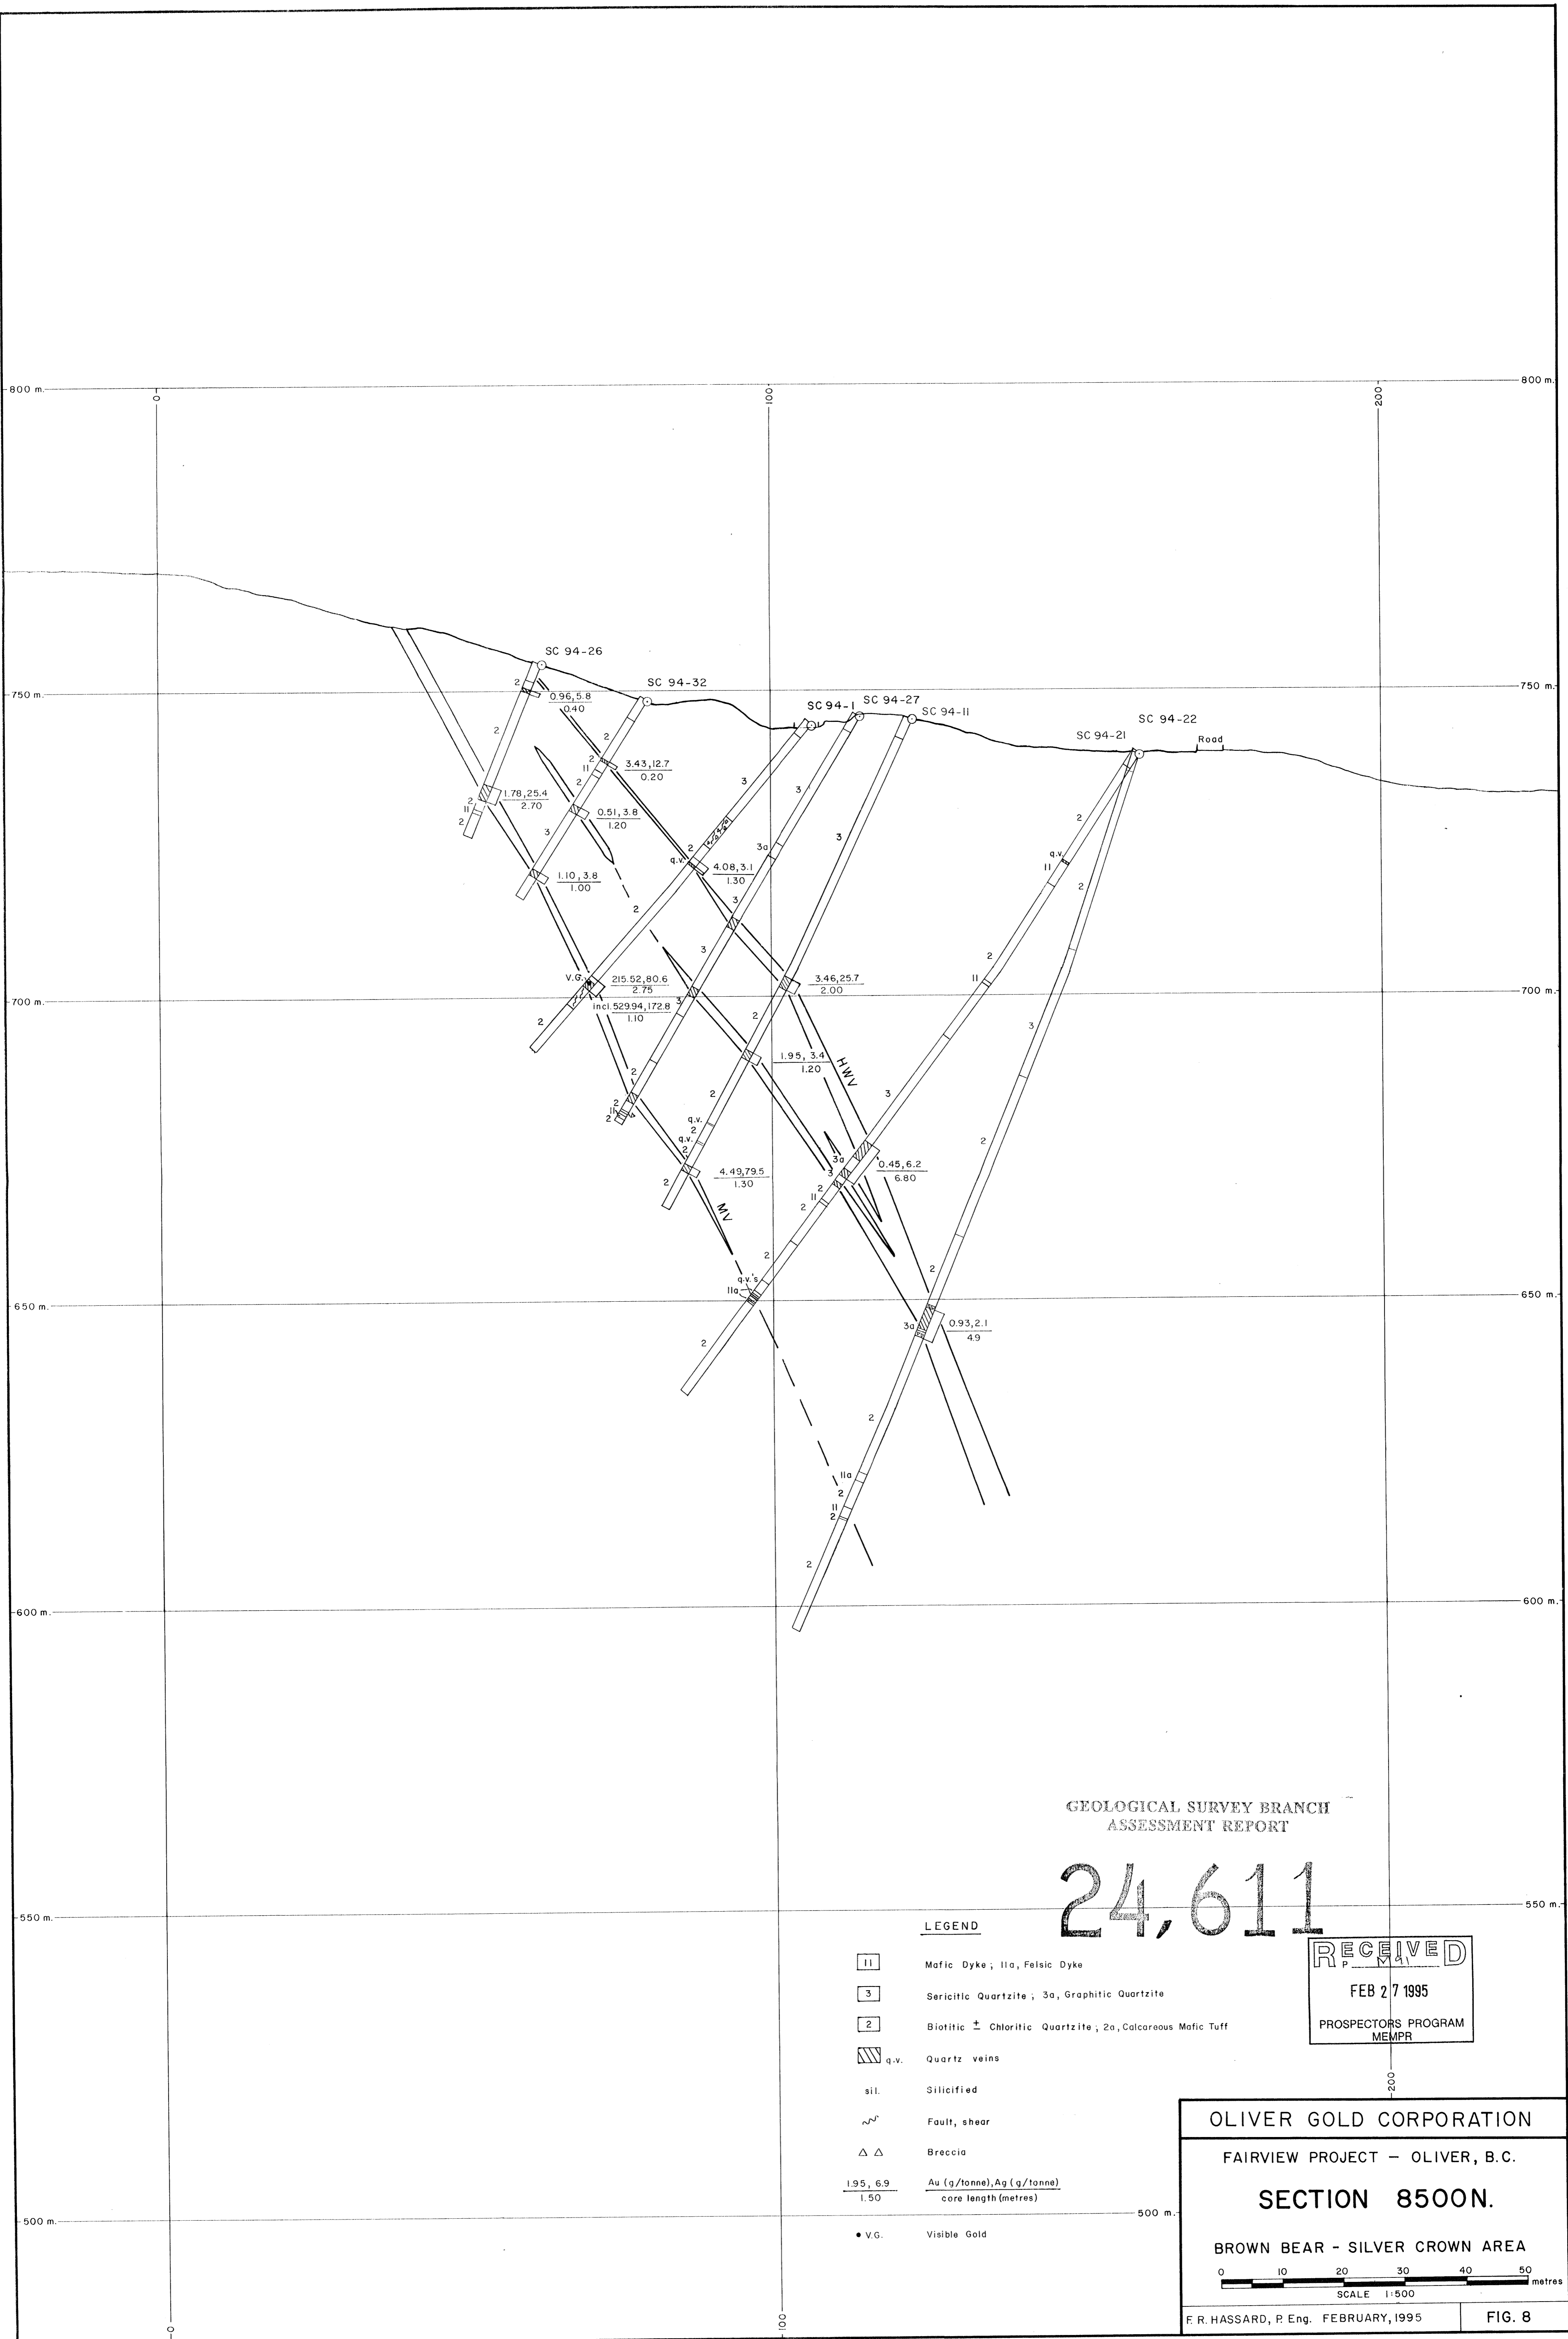

GEOLOGICAL SURVEY BRANCH
ASSESSMENT REPORT

24,611

LEGEND

- 1 Mafic Dyke; 11a, Felsic Dyke
- 3 Sericitic Quartzite; 3a, Graphitic Quartzite
- 2 Biotitic ± Chloritic Quartzite; 2a, Calcareous Mafic Tuff
- q.v. Quartz veins
- sil. Silicified
- ~ Fault, shear
- △ Breccia
- $\frac{1.95, 6.9}{1.50}$ Au (g/tonne), Ag (g/tonne)
core length (metres)
- V.G. Visible Gold


RECEIVED
FEB 27 1995
PROSPECTORS PROGRAM
MEMPR

OLIVER GOLD CORPORATION
FAIRVIEW PROJECT - OLIVER, B.C.
SECTION 8500N.
BROWN BEAR - SILVER CROWN AREA

0 10 20 30 40 50 metres
SCALE 1:500

F.R. HASSARD, P. Eng. FEBRUARY, 1995

FIG. 8

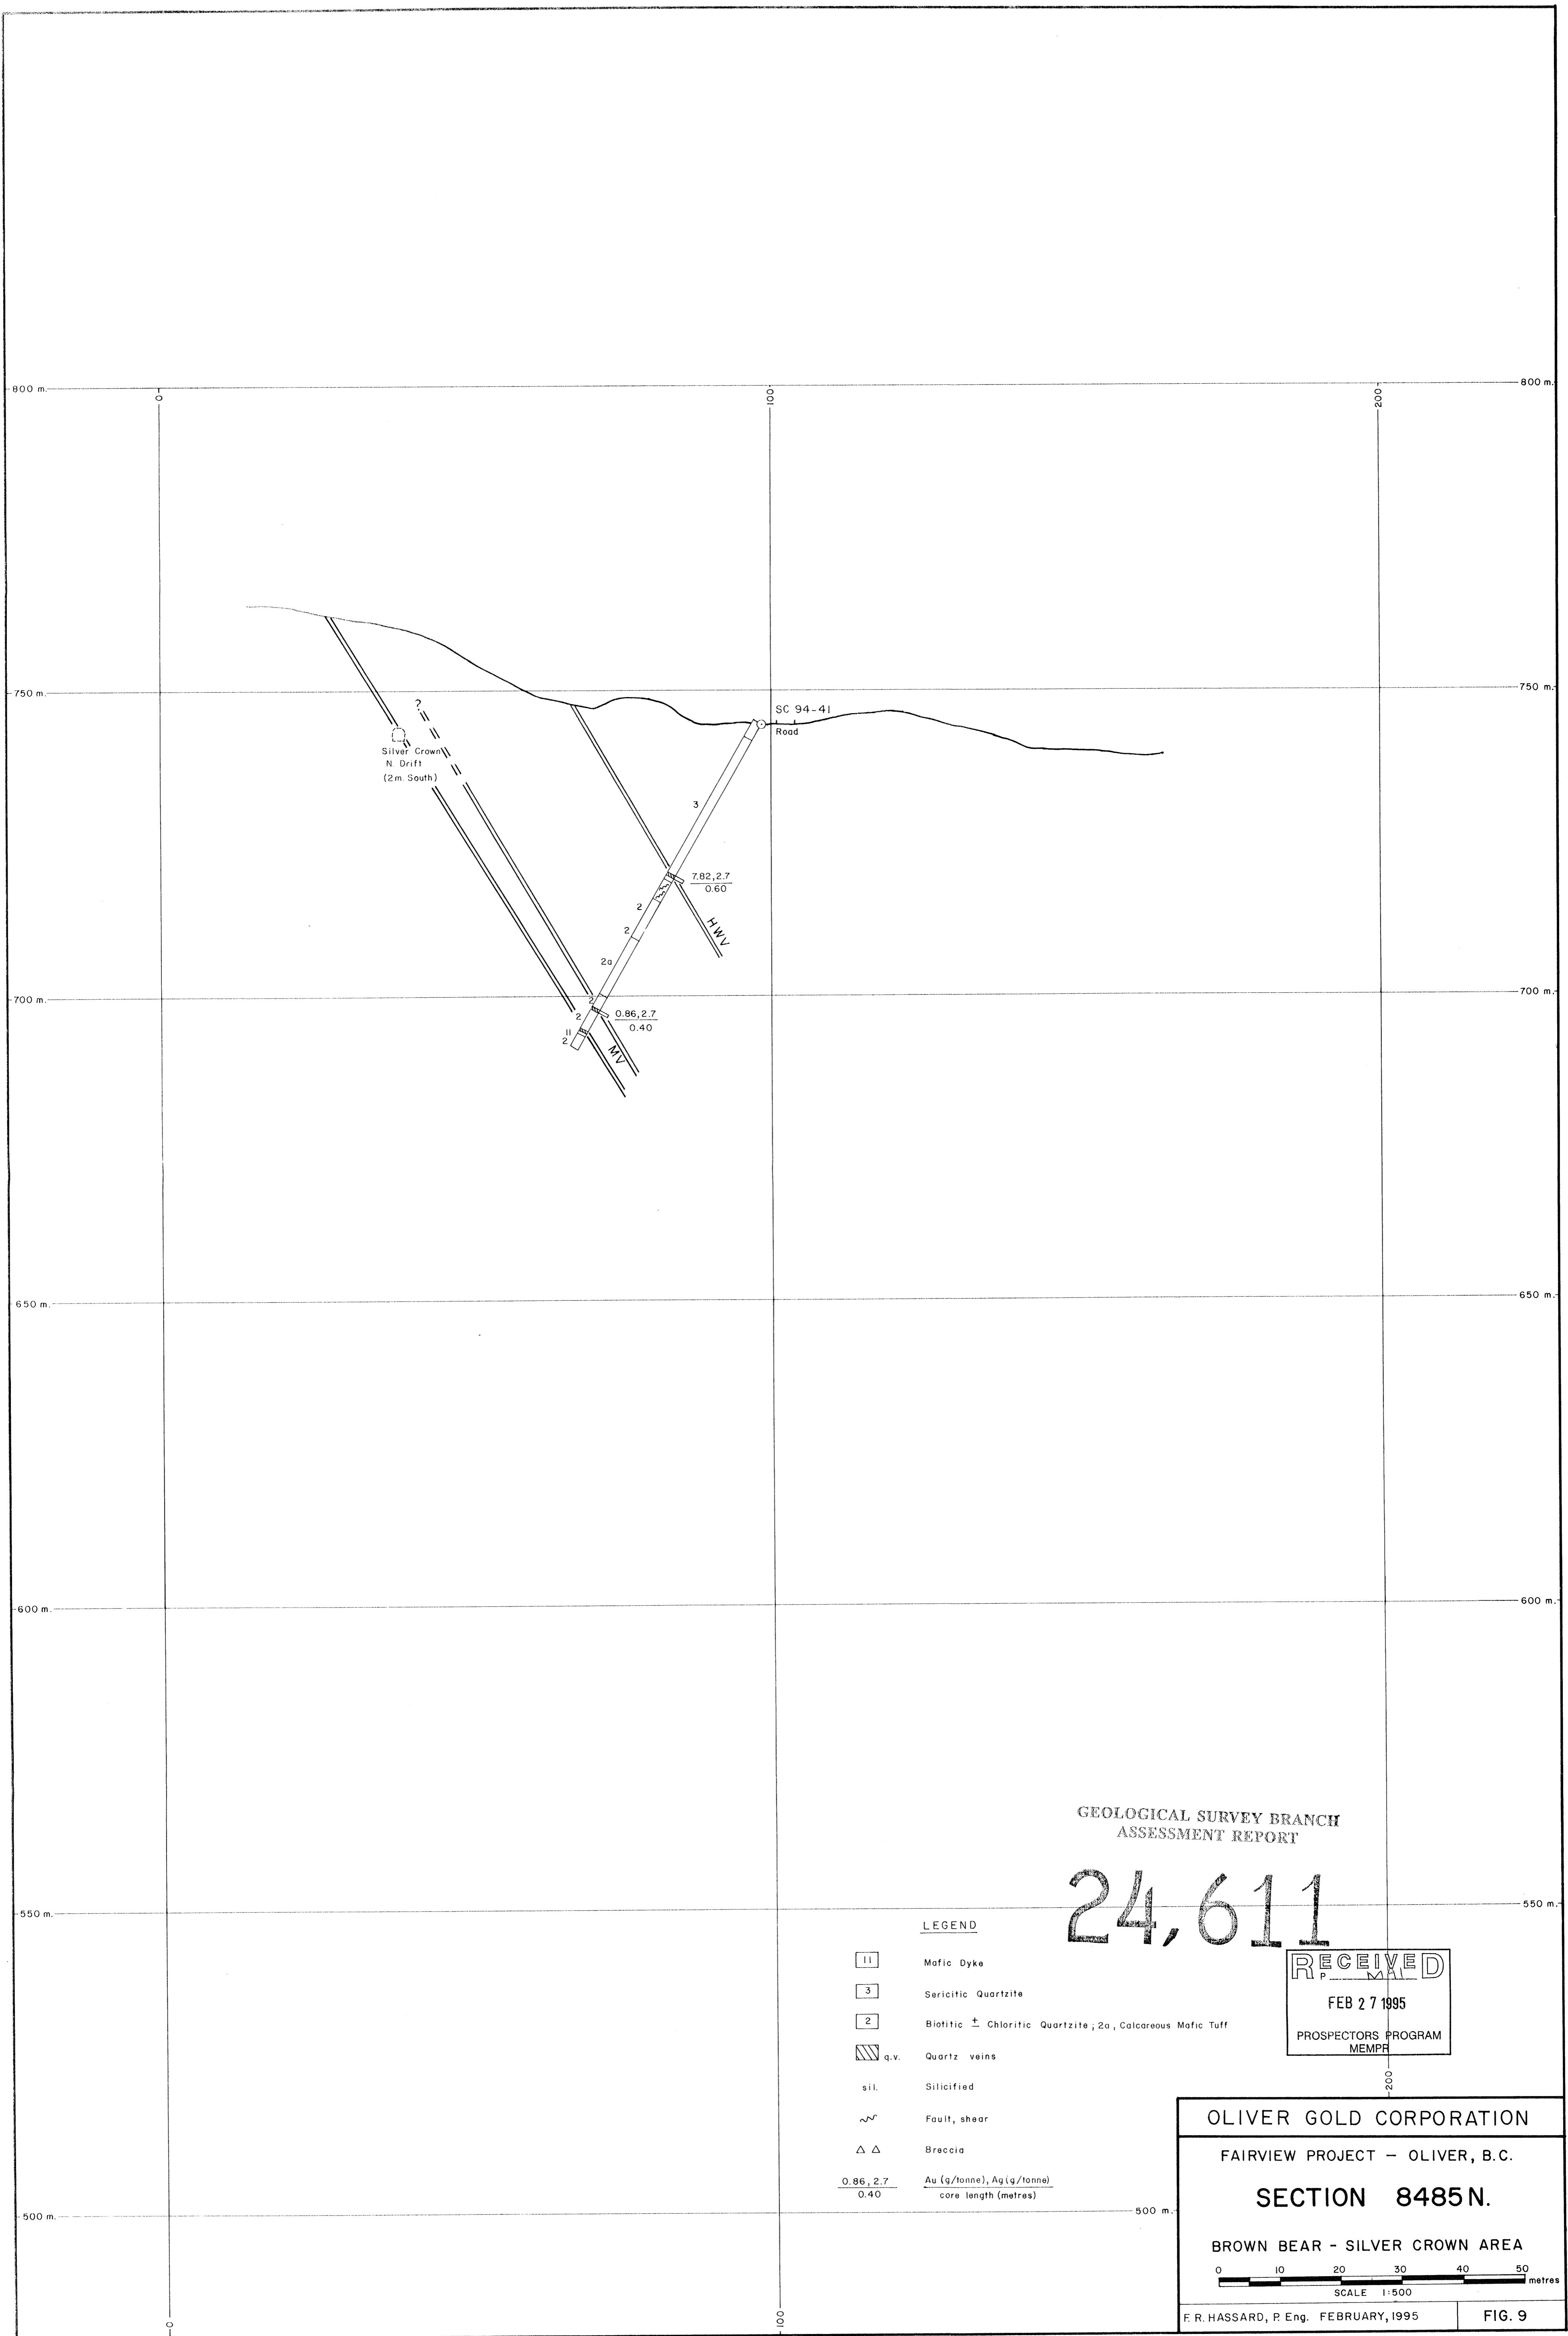

GEOLOGICAL SURVEY BRANCH
ASSESSMENT REPORT

24,611

- LEGEND
- 1 Mafic Dyke
 - 3 Sericitic Quartzite
 - 2 Biotitic ± Chloritic Quartzite, 2a, Calcareous Mafic Tuff
 - q.v. Quartz veins
 - sil. Silicified
 - ~ Fault, shear
 - △△ Breccia
 - $\frac{0.86, 2.7}{0.40}$ Au (g/tonne), Ag (g/tonne)
core length (metres)

RECEIVED
FEB 27 1995
PROSPECTORS PROGRAM
MEMPH

OLIVER GOLD CORPORATION

FAIRVIEW PROJECT - OLIVER, B.C.


SECTION 8485N.

BROWN BEAR - SILVER CROWN AREA

0 10 20 30 40 50 metres
SCALE 1:500

F. R. HASSARD, P. Eng. FEBRUARY, 1995

FIG. 9

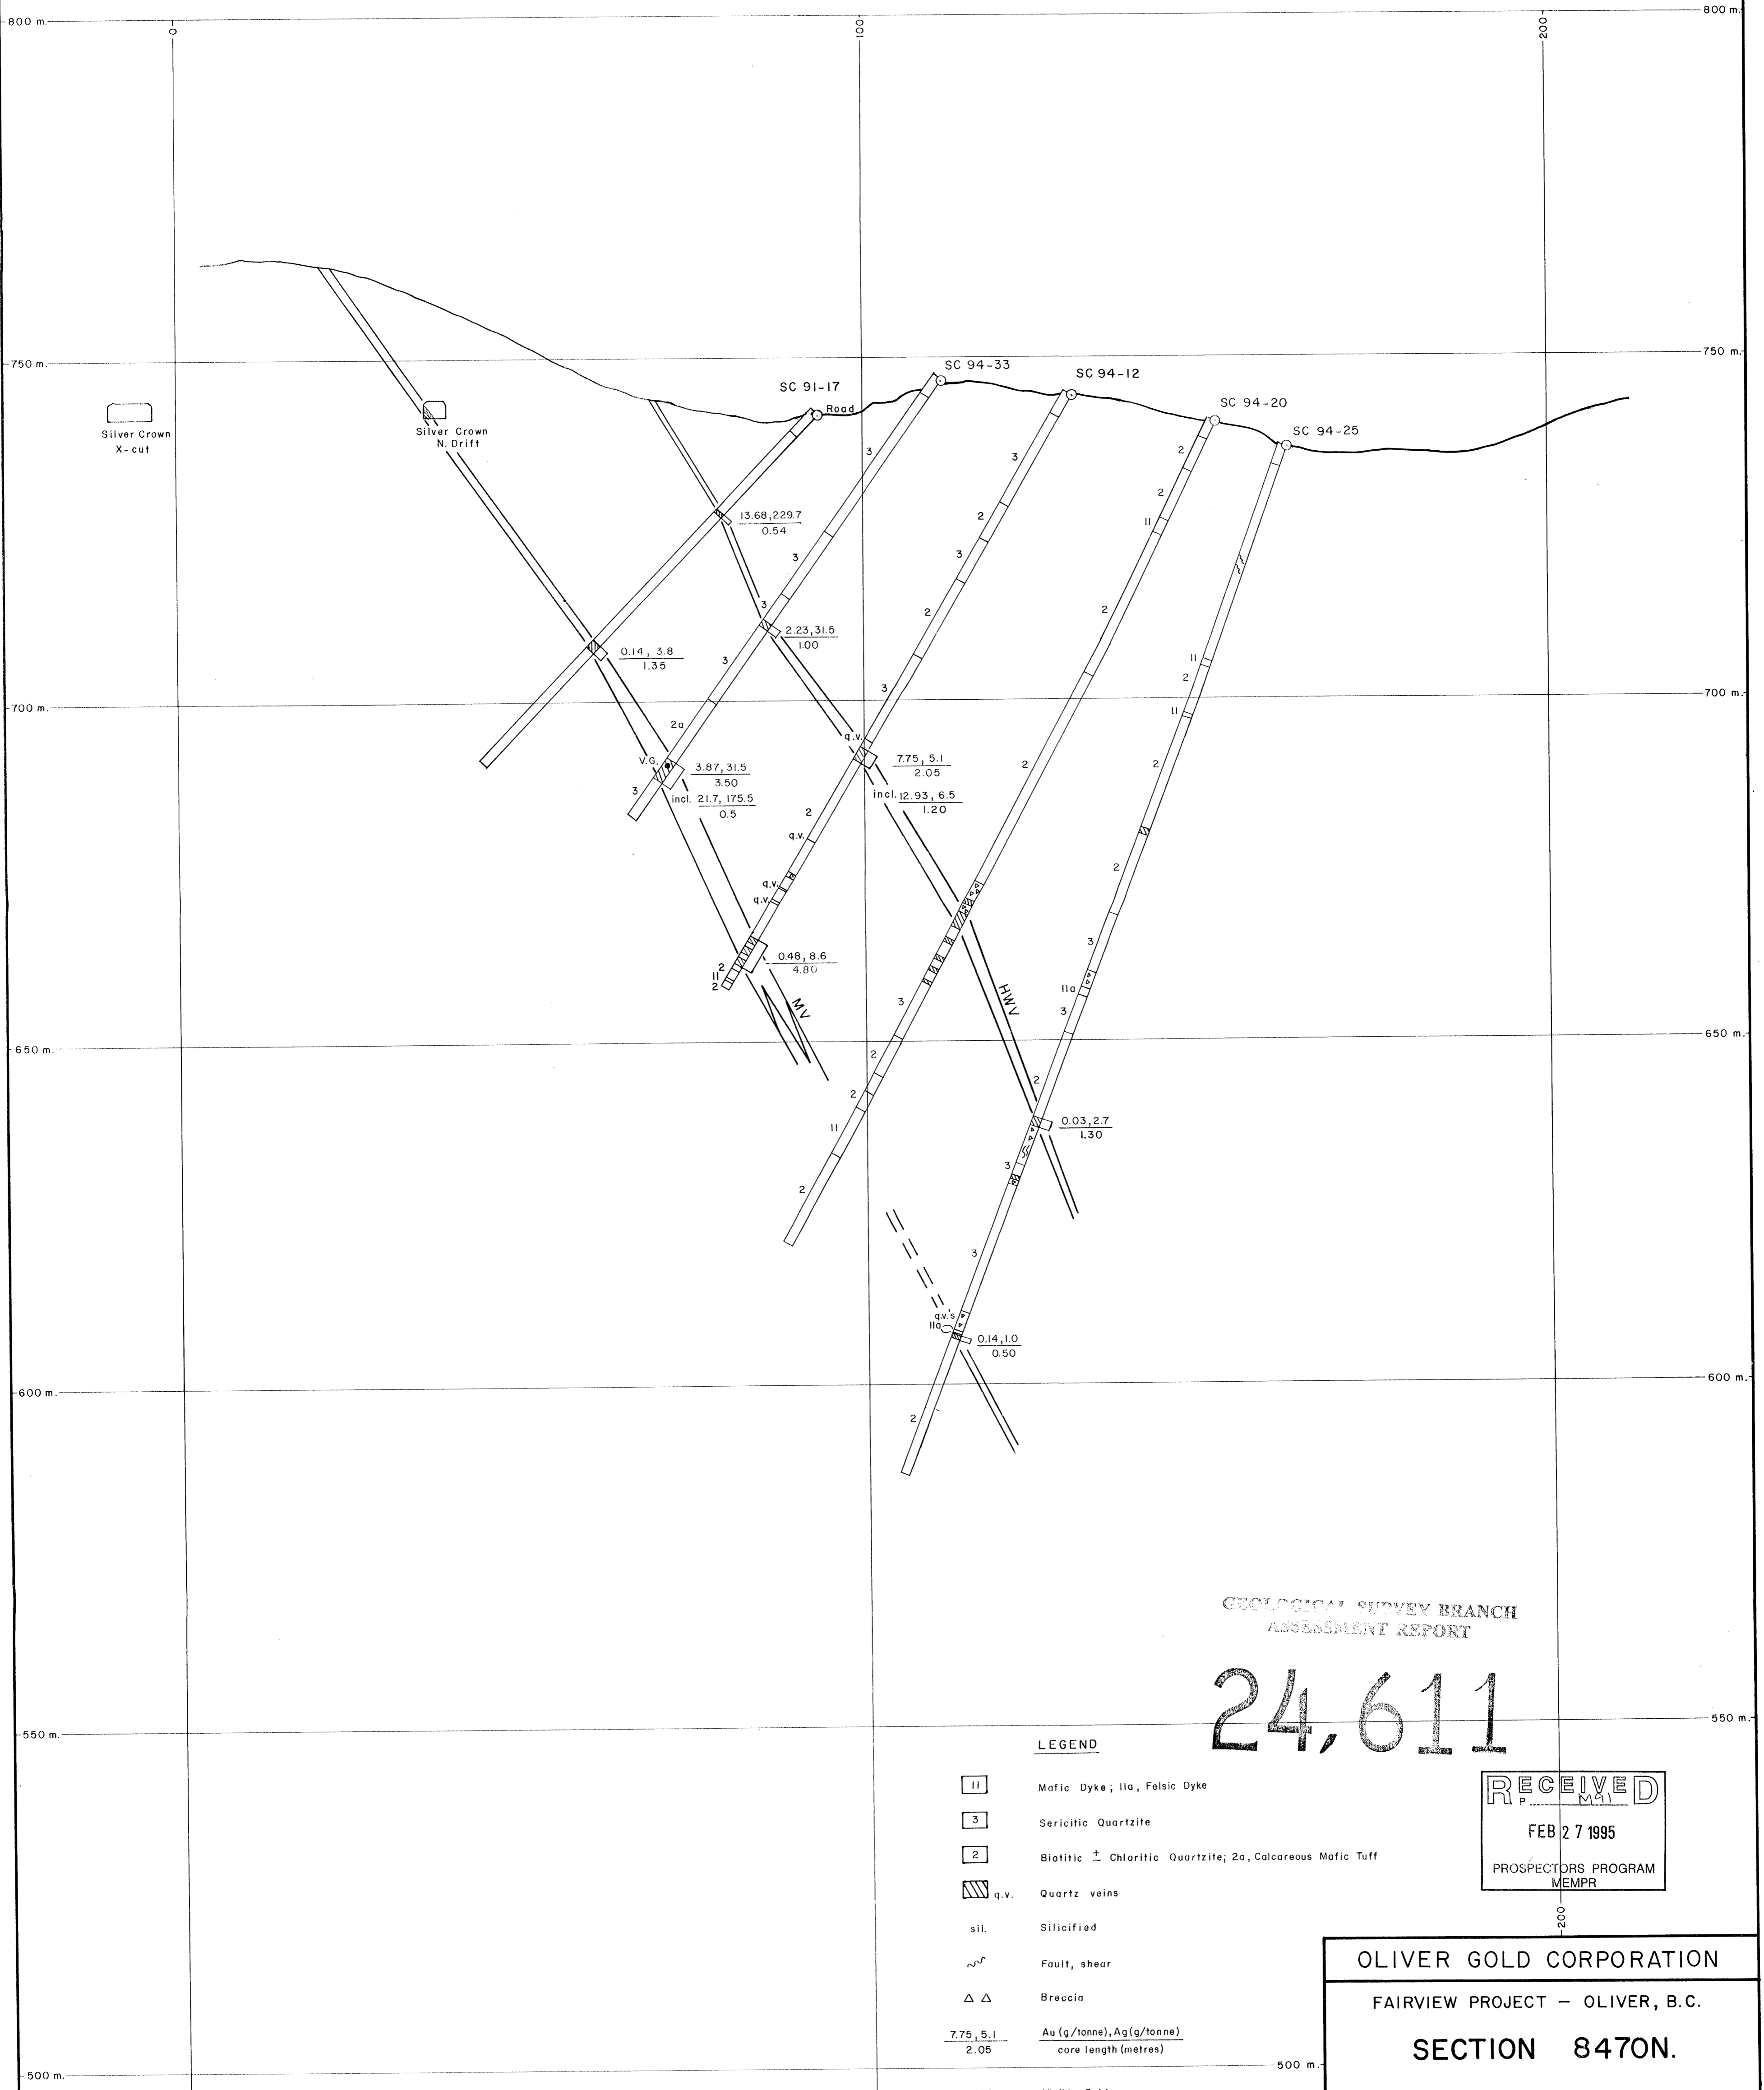

GEOLOGICAL SURVEY BRANCH
ASSESSMENT REPORT

24,611

LEGEND

- 11 Mafic Dyke; Ila, Felsic Dyke
- 3 Sericitic Quartzite
- 2 Biotitic ± Chloritic Quartzite; 2a, Calcareous Mafic Tuff
- q.v. Quartz veins
- sil. Silicified
- ~ Fault, shear
- △△ Breccia
- $\frac{7.75, 5.1}{2.05}$ Au (g/tonne), Ag (g/tonne)
core length (metres)
- V.G. Visible Gold


RECEIVED
FEB 27 1995
PROSPECTORS PROGRAM
MEMPR

OLIVER GOLD CORPORATION
FAIRVIEW PROJECT - OLIVER, B.C.
SECTION 8470N.
BROWN BEAR - SILVER CROWN AREA

0 10 20 30 40 50 metres
SCALE 1:500

F. R. HASSARD, P. Eng. FEBRUARY, 1995

FIG. 10

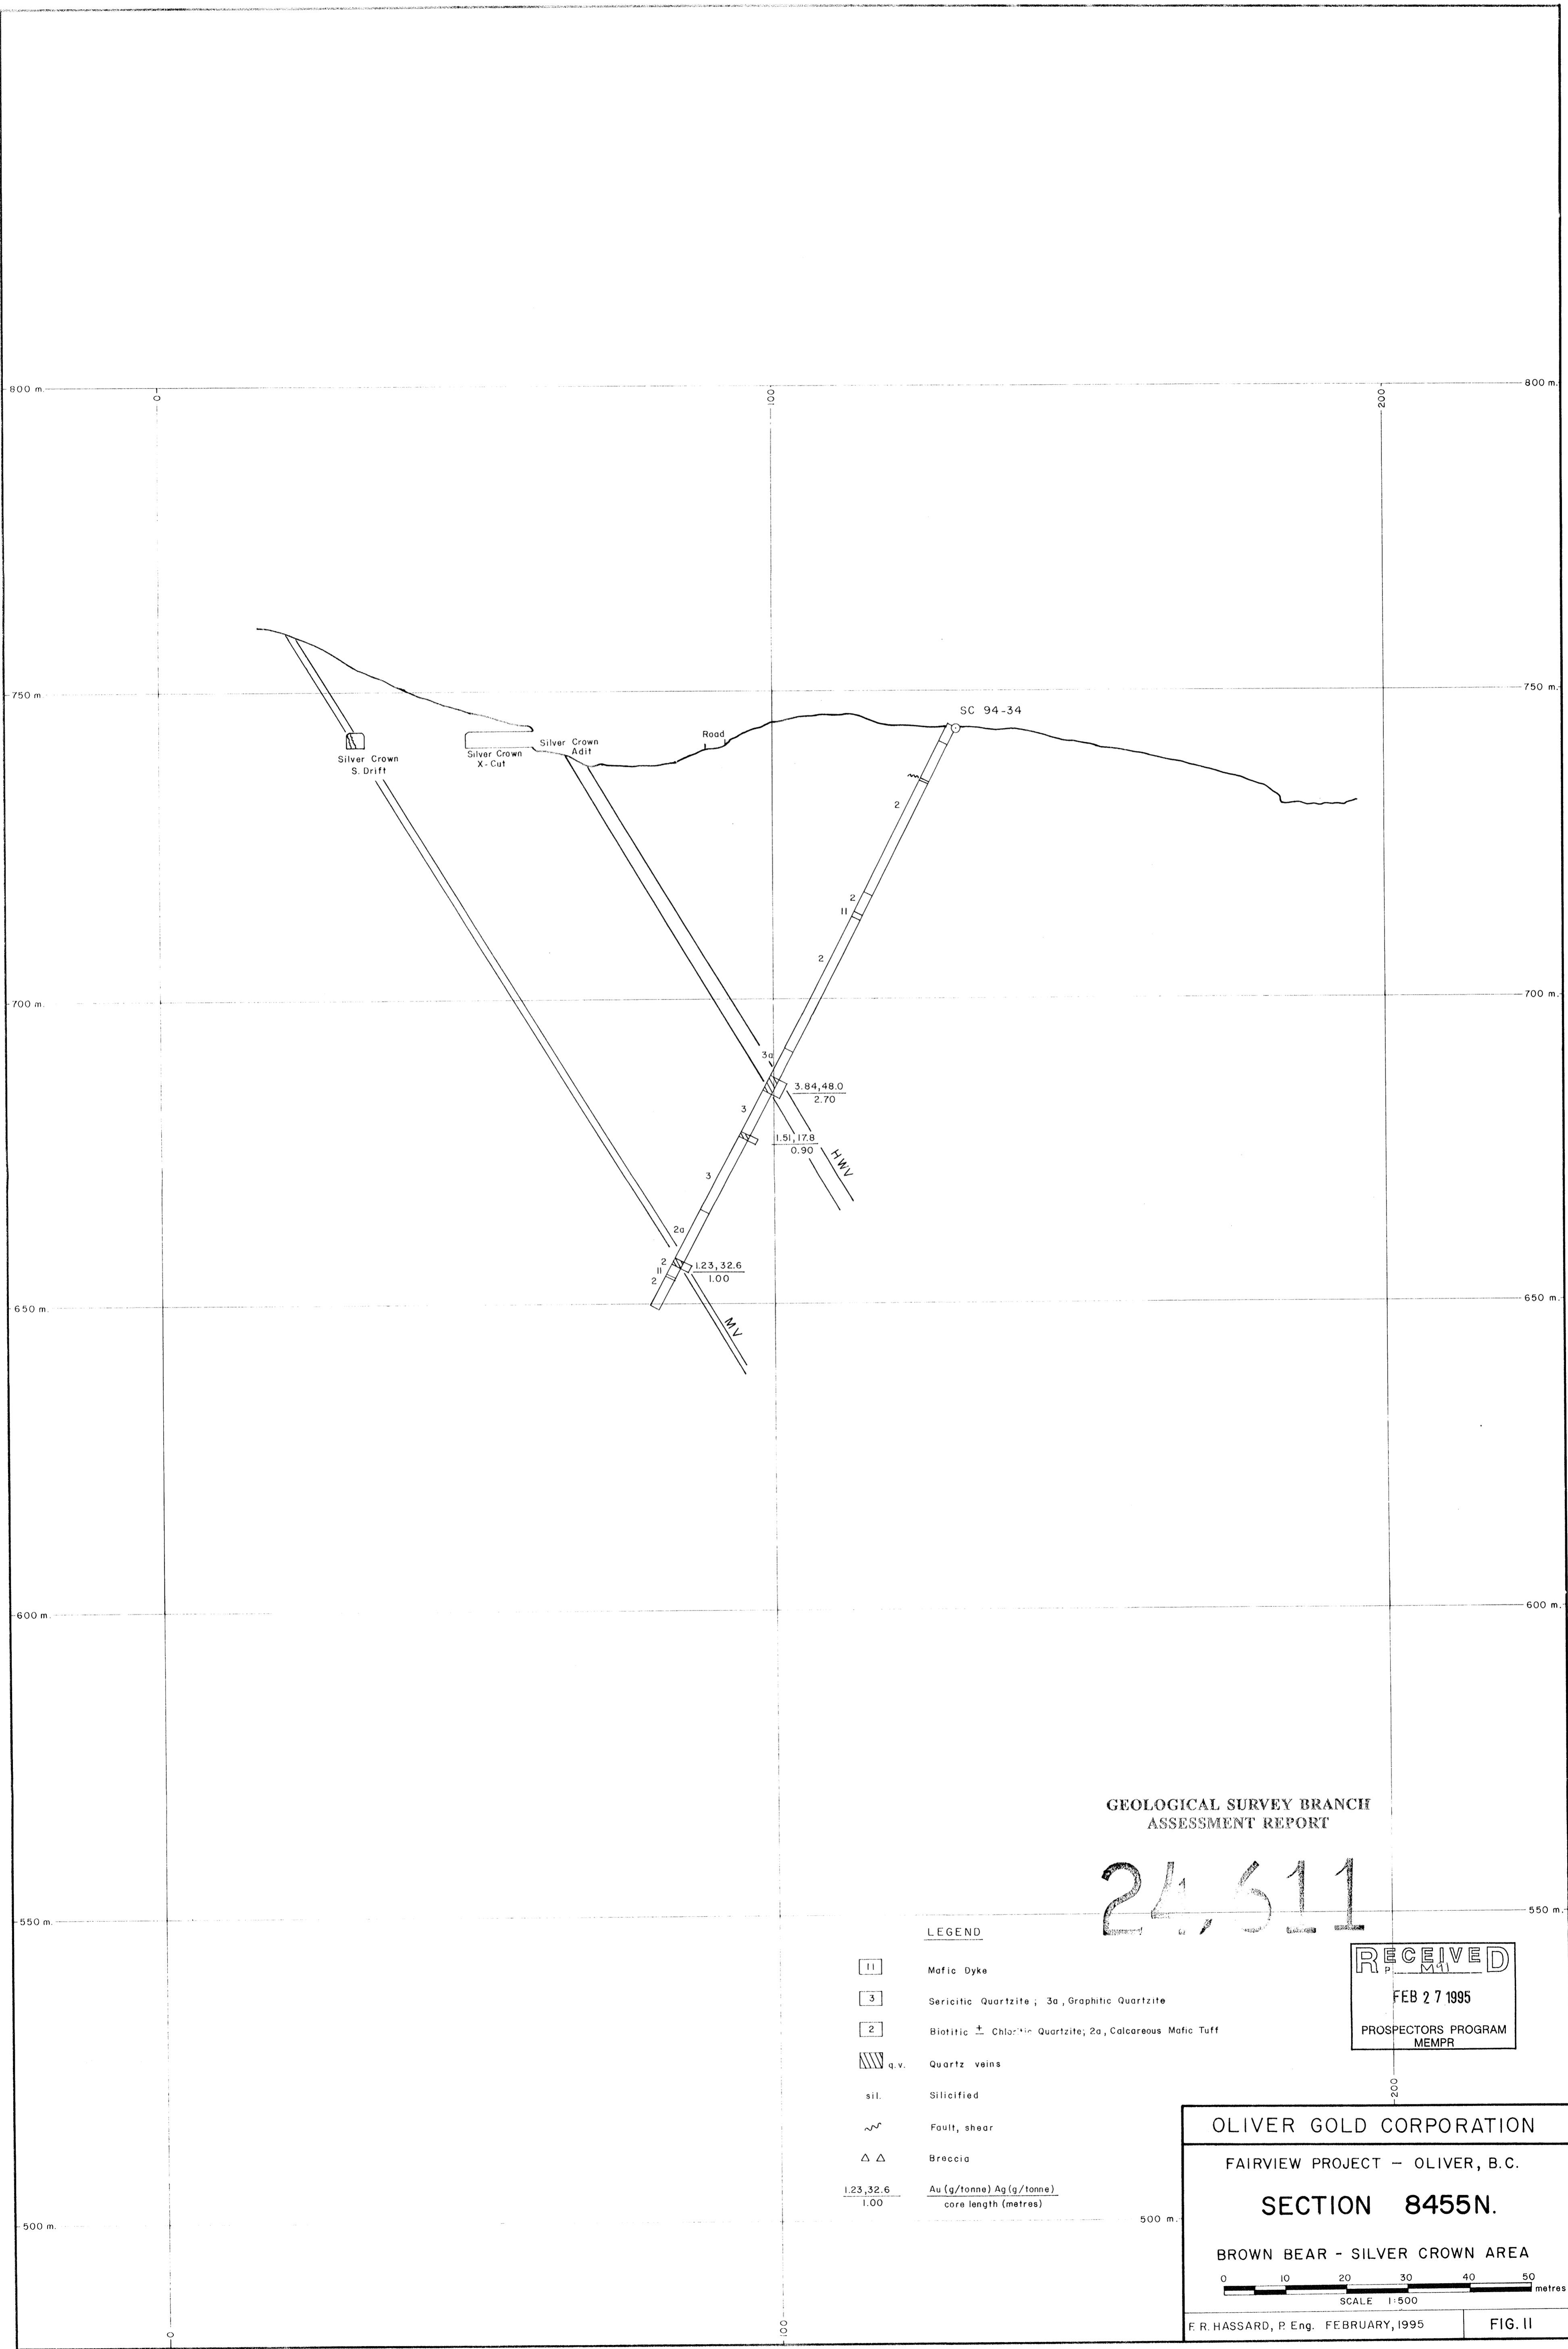

GEOLOGICAL SURVEY BRANCH
ASSESSMENT REPORT

24,511

LEGEND

- [1] Mafic Dyke
 - [3] Sericitic Quartzite; 3a, Graphitic Quartzite
 - [2] Biotitic ± Chloritic Quartzite; 2a, Calcareous Mafic Tuff
 - q.v. Quartz veins
 - sil. Silicified
 - ~ Fault, shear
 - △ Breccia
- | | |
|------------|---------------------------|
| 1.23, 32.6 | Au (g/tonne) Ag (g/tonne) |
| 1.00 | core length (metres) |


RECEIVED
FEB 27 1995
PROSPECTORS PROGRAM
MEMPR

OLIVER GOLD CORPORATION

FAIRVIEW PROJECT - OLIVER, B.C.


SECTION 8455N.

BROWN BEAR - SILVER CROWN AREA



F.R. HASSARD, P. Eng. FEBRUARY, 1995

FIG. II

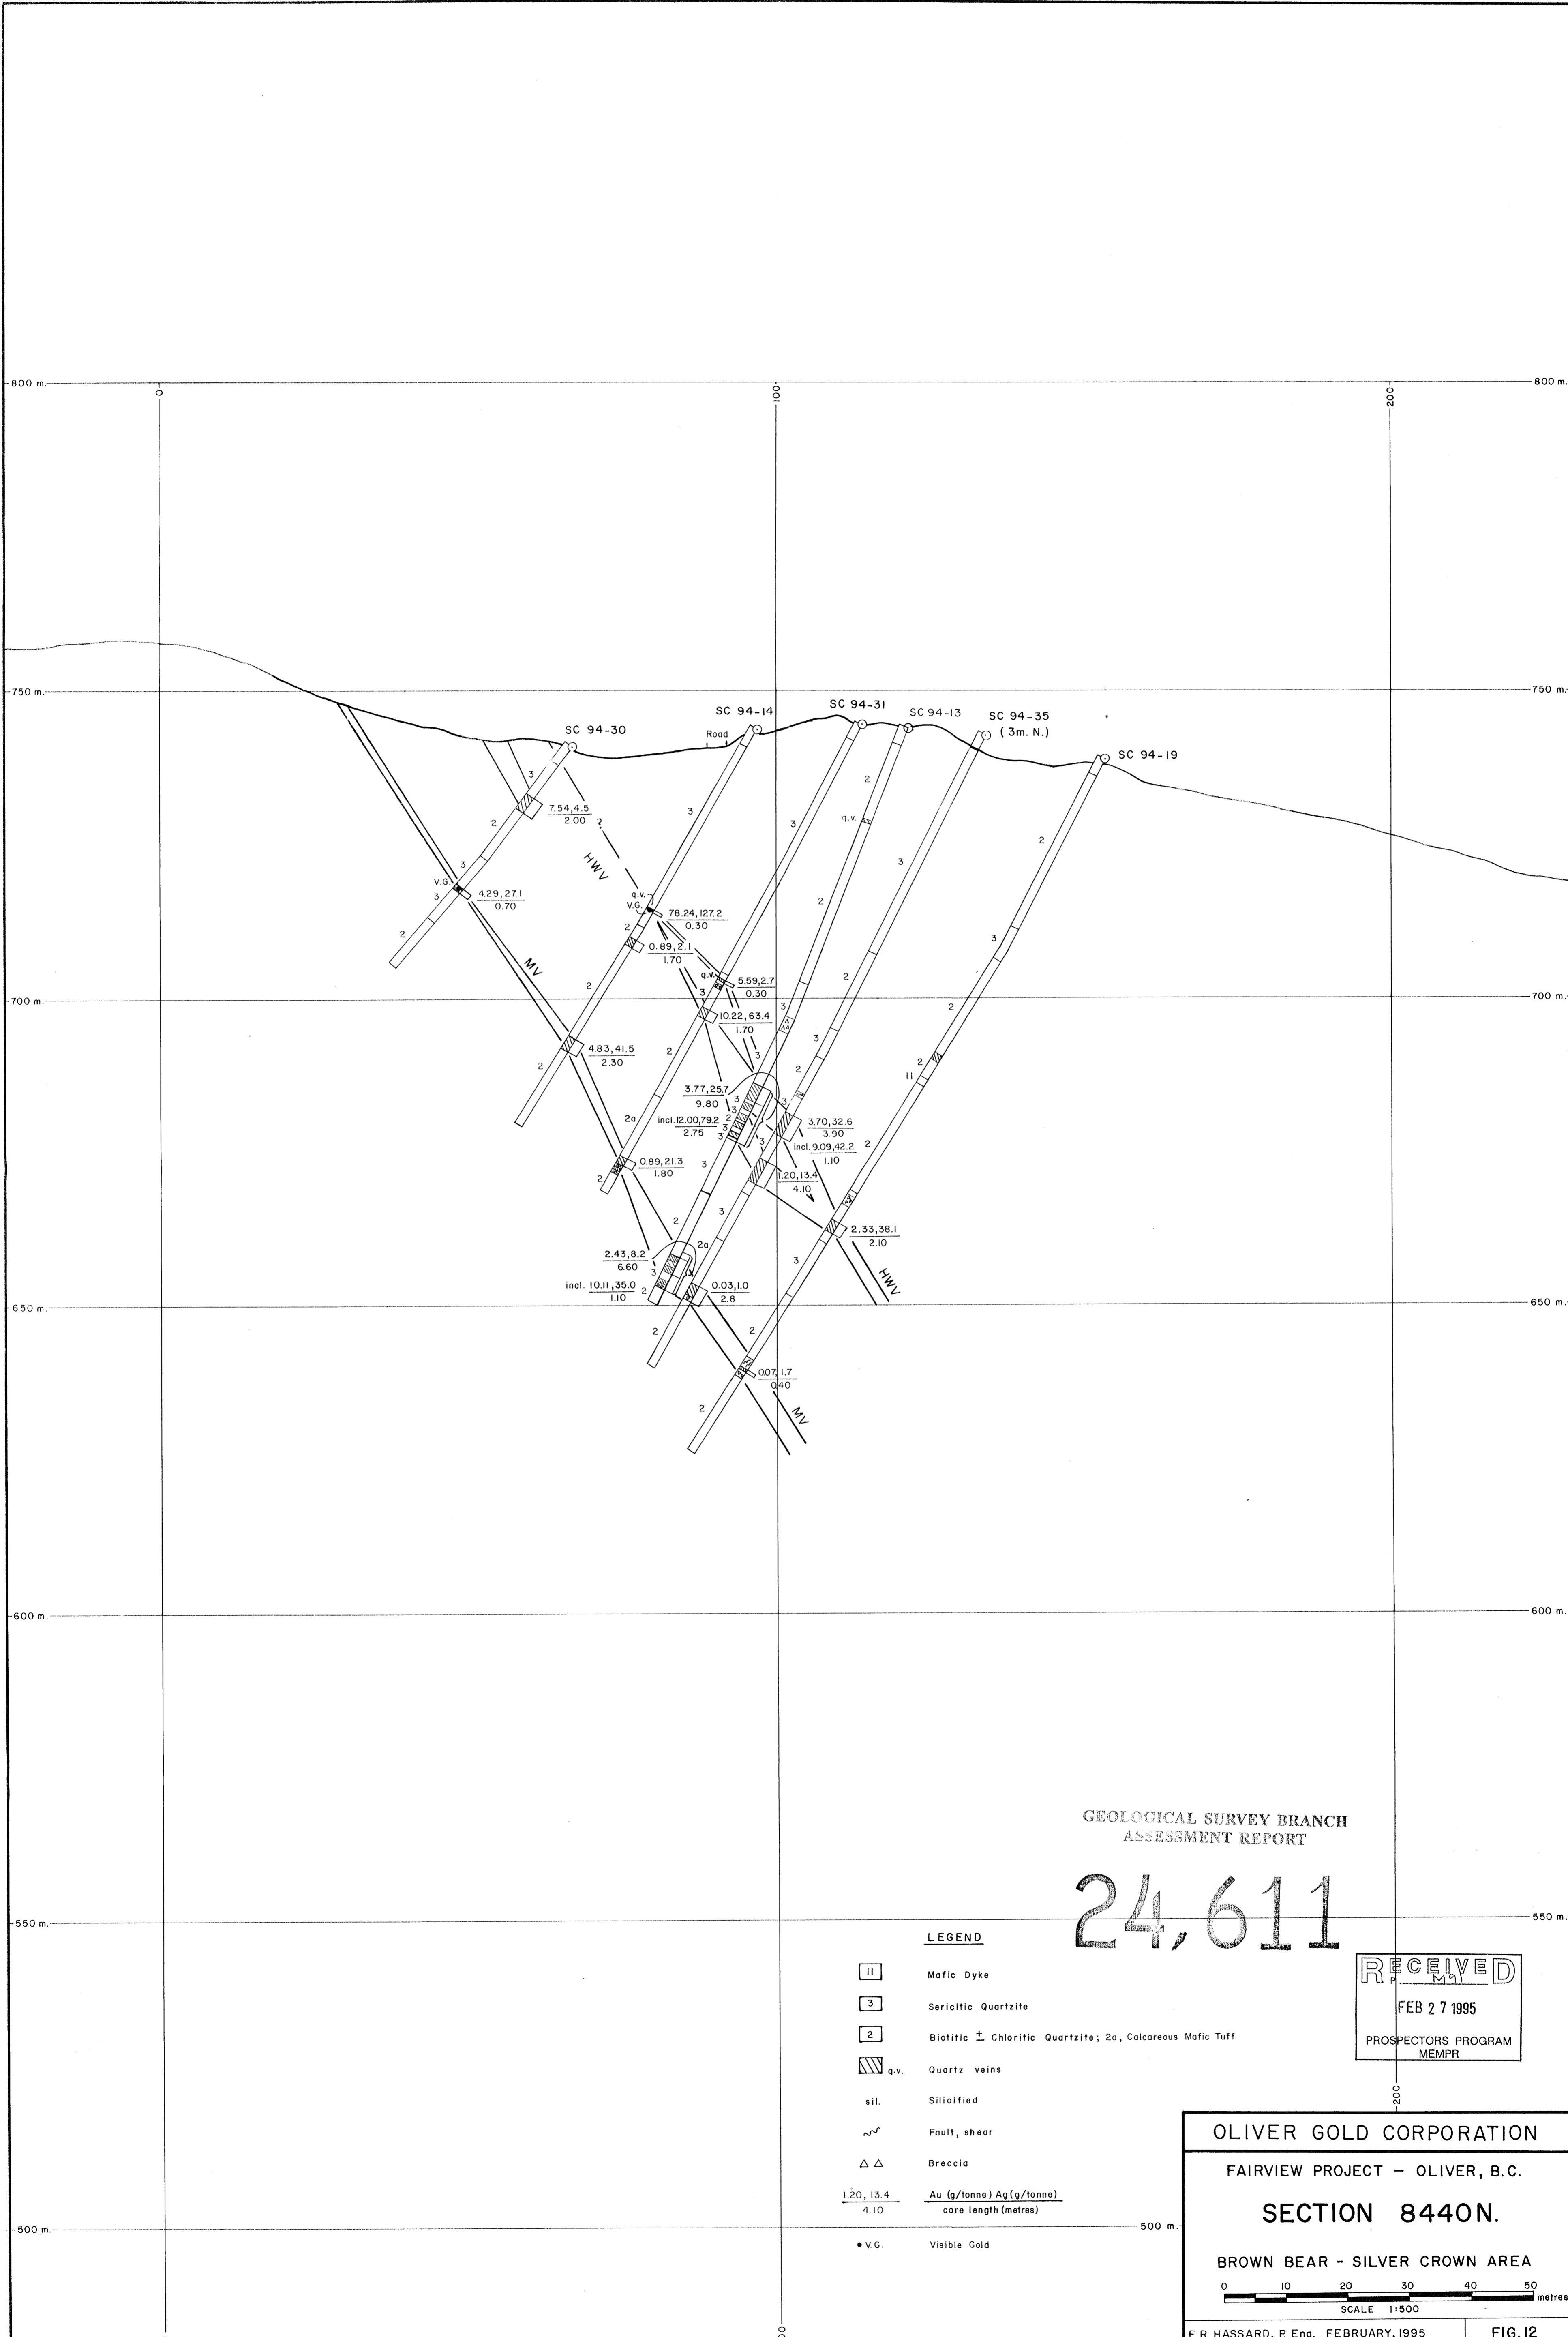

GEOLOGICAL SURVEY BRANCH
ASSESSMENT REPORT

24,611


LEGEND

- ▬ Mafic Dyke
- ▭ Sericitic Quartzite
- ▭ Biotitic ± Chloritic Quartzite; 2a, Calcareous Mafic Tuff
- ▨ q.v. Quartz veins
- sil. Silicified
- ~ Fault, shear
- △△ Breccia
- $\frac{1.20, 13.4}{4.10}$ Au (g/tonne) Ag (g/tonne)
core length (metres)
- V.G. Visible Gold

RECEIVED
FEB 27 1995
PROSPECTORS PROGRAM
MEMPR

OLIVER GOLD CORPORATION
FAIRVIEW PROJECT - OLIVER, B.C.
SECTION 8440N.

BROWN BEAR - SILVER CROWN AREA
0 10 20 30 40 50 metres
SCALE 1:500

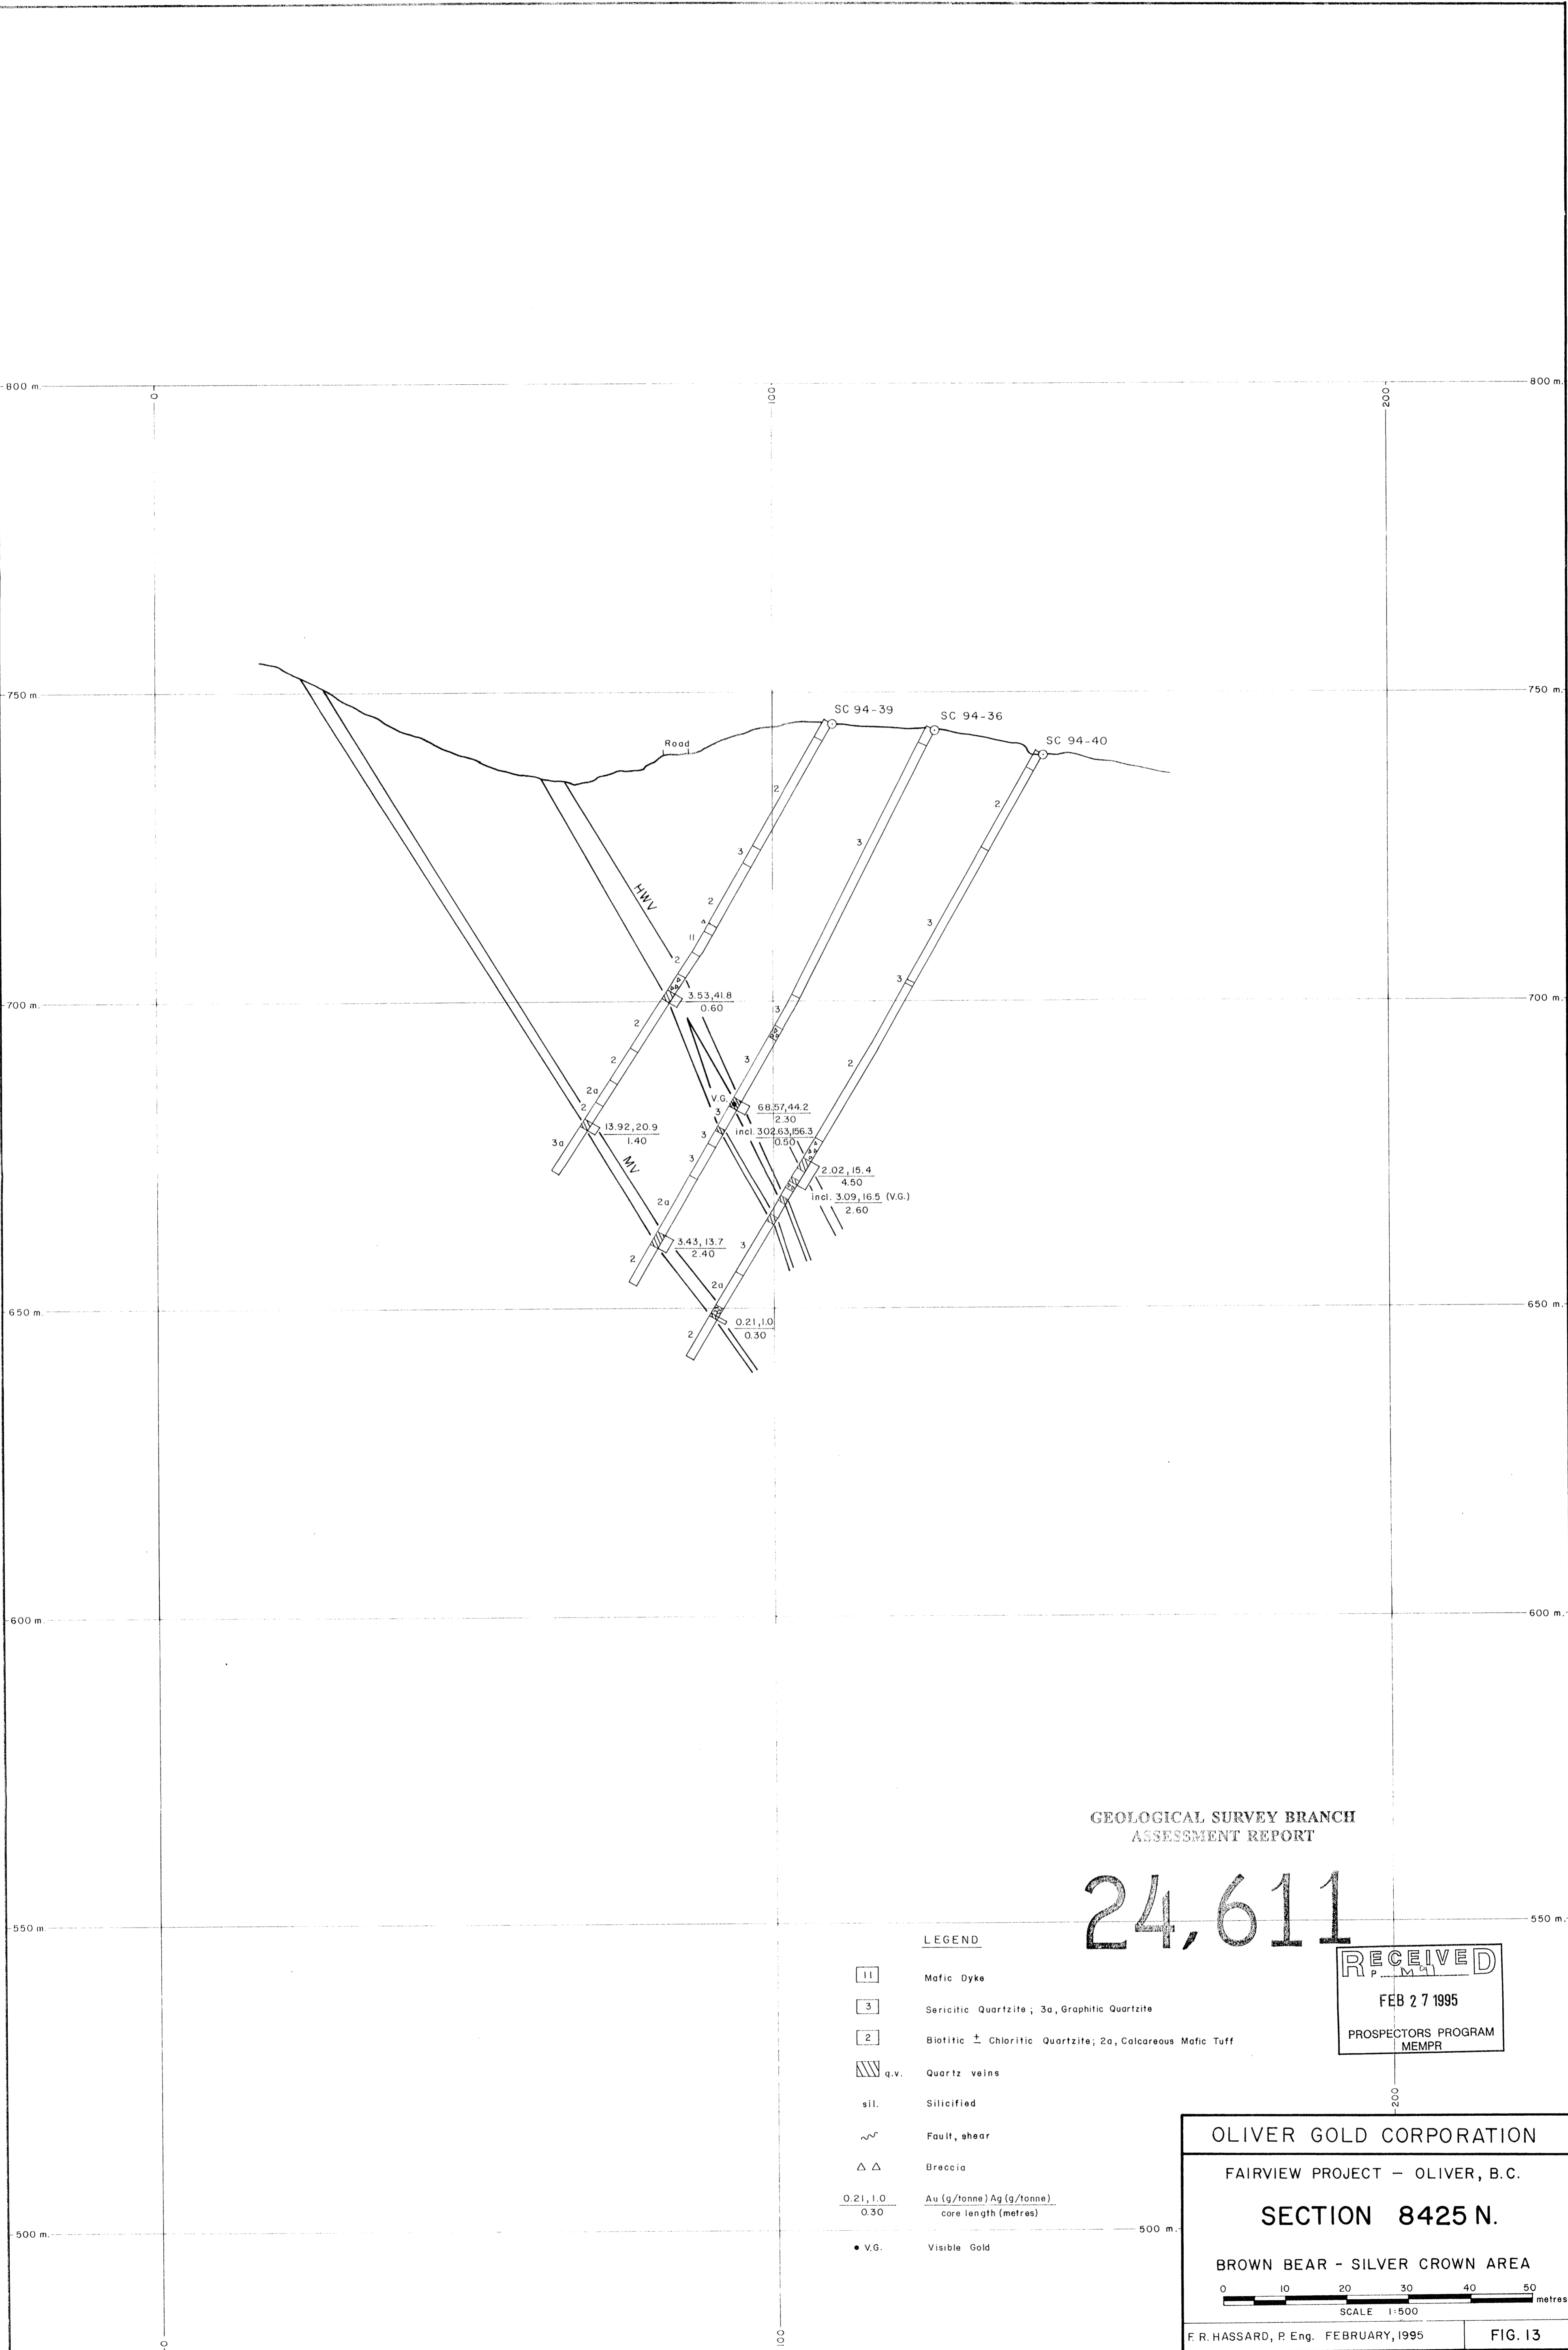

GEOLOGICAL SURVEY BRANCH
ASSESSMENT REPORT

24,611


LEGEND

- 11 Mafic Dyke
- 3 Sericitic Quartzite; 3a, Graphitic Quartzite
- 2 Biotitic ± Chloritic Quartzite; 2a, Calcareous Mafic Tuff
- q.v. Quartz veins
- sil. Silicified
- ~ Fault, shear
- △ Breccia
- 0.21, 1.0 / 0.30 Au (g/tonne) Ag (g/tonne) / core length (metres)
- V.G. Visible Gold

RECEIVED
FEB 27 1995
PROSPECTORS PROGRAM
MEMPR

OLIVER GOLD CORPORATION
FAIRVIEW PROJECT - OLIVER, B.C.
SECTION 8425 N.

BROWN BEAR - SILVER CROWN AREA
0 10 20 30 40 50 metres
SCALE 1:500

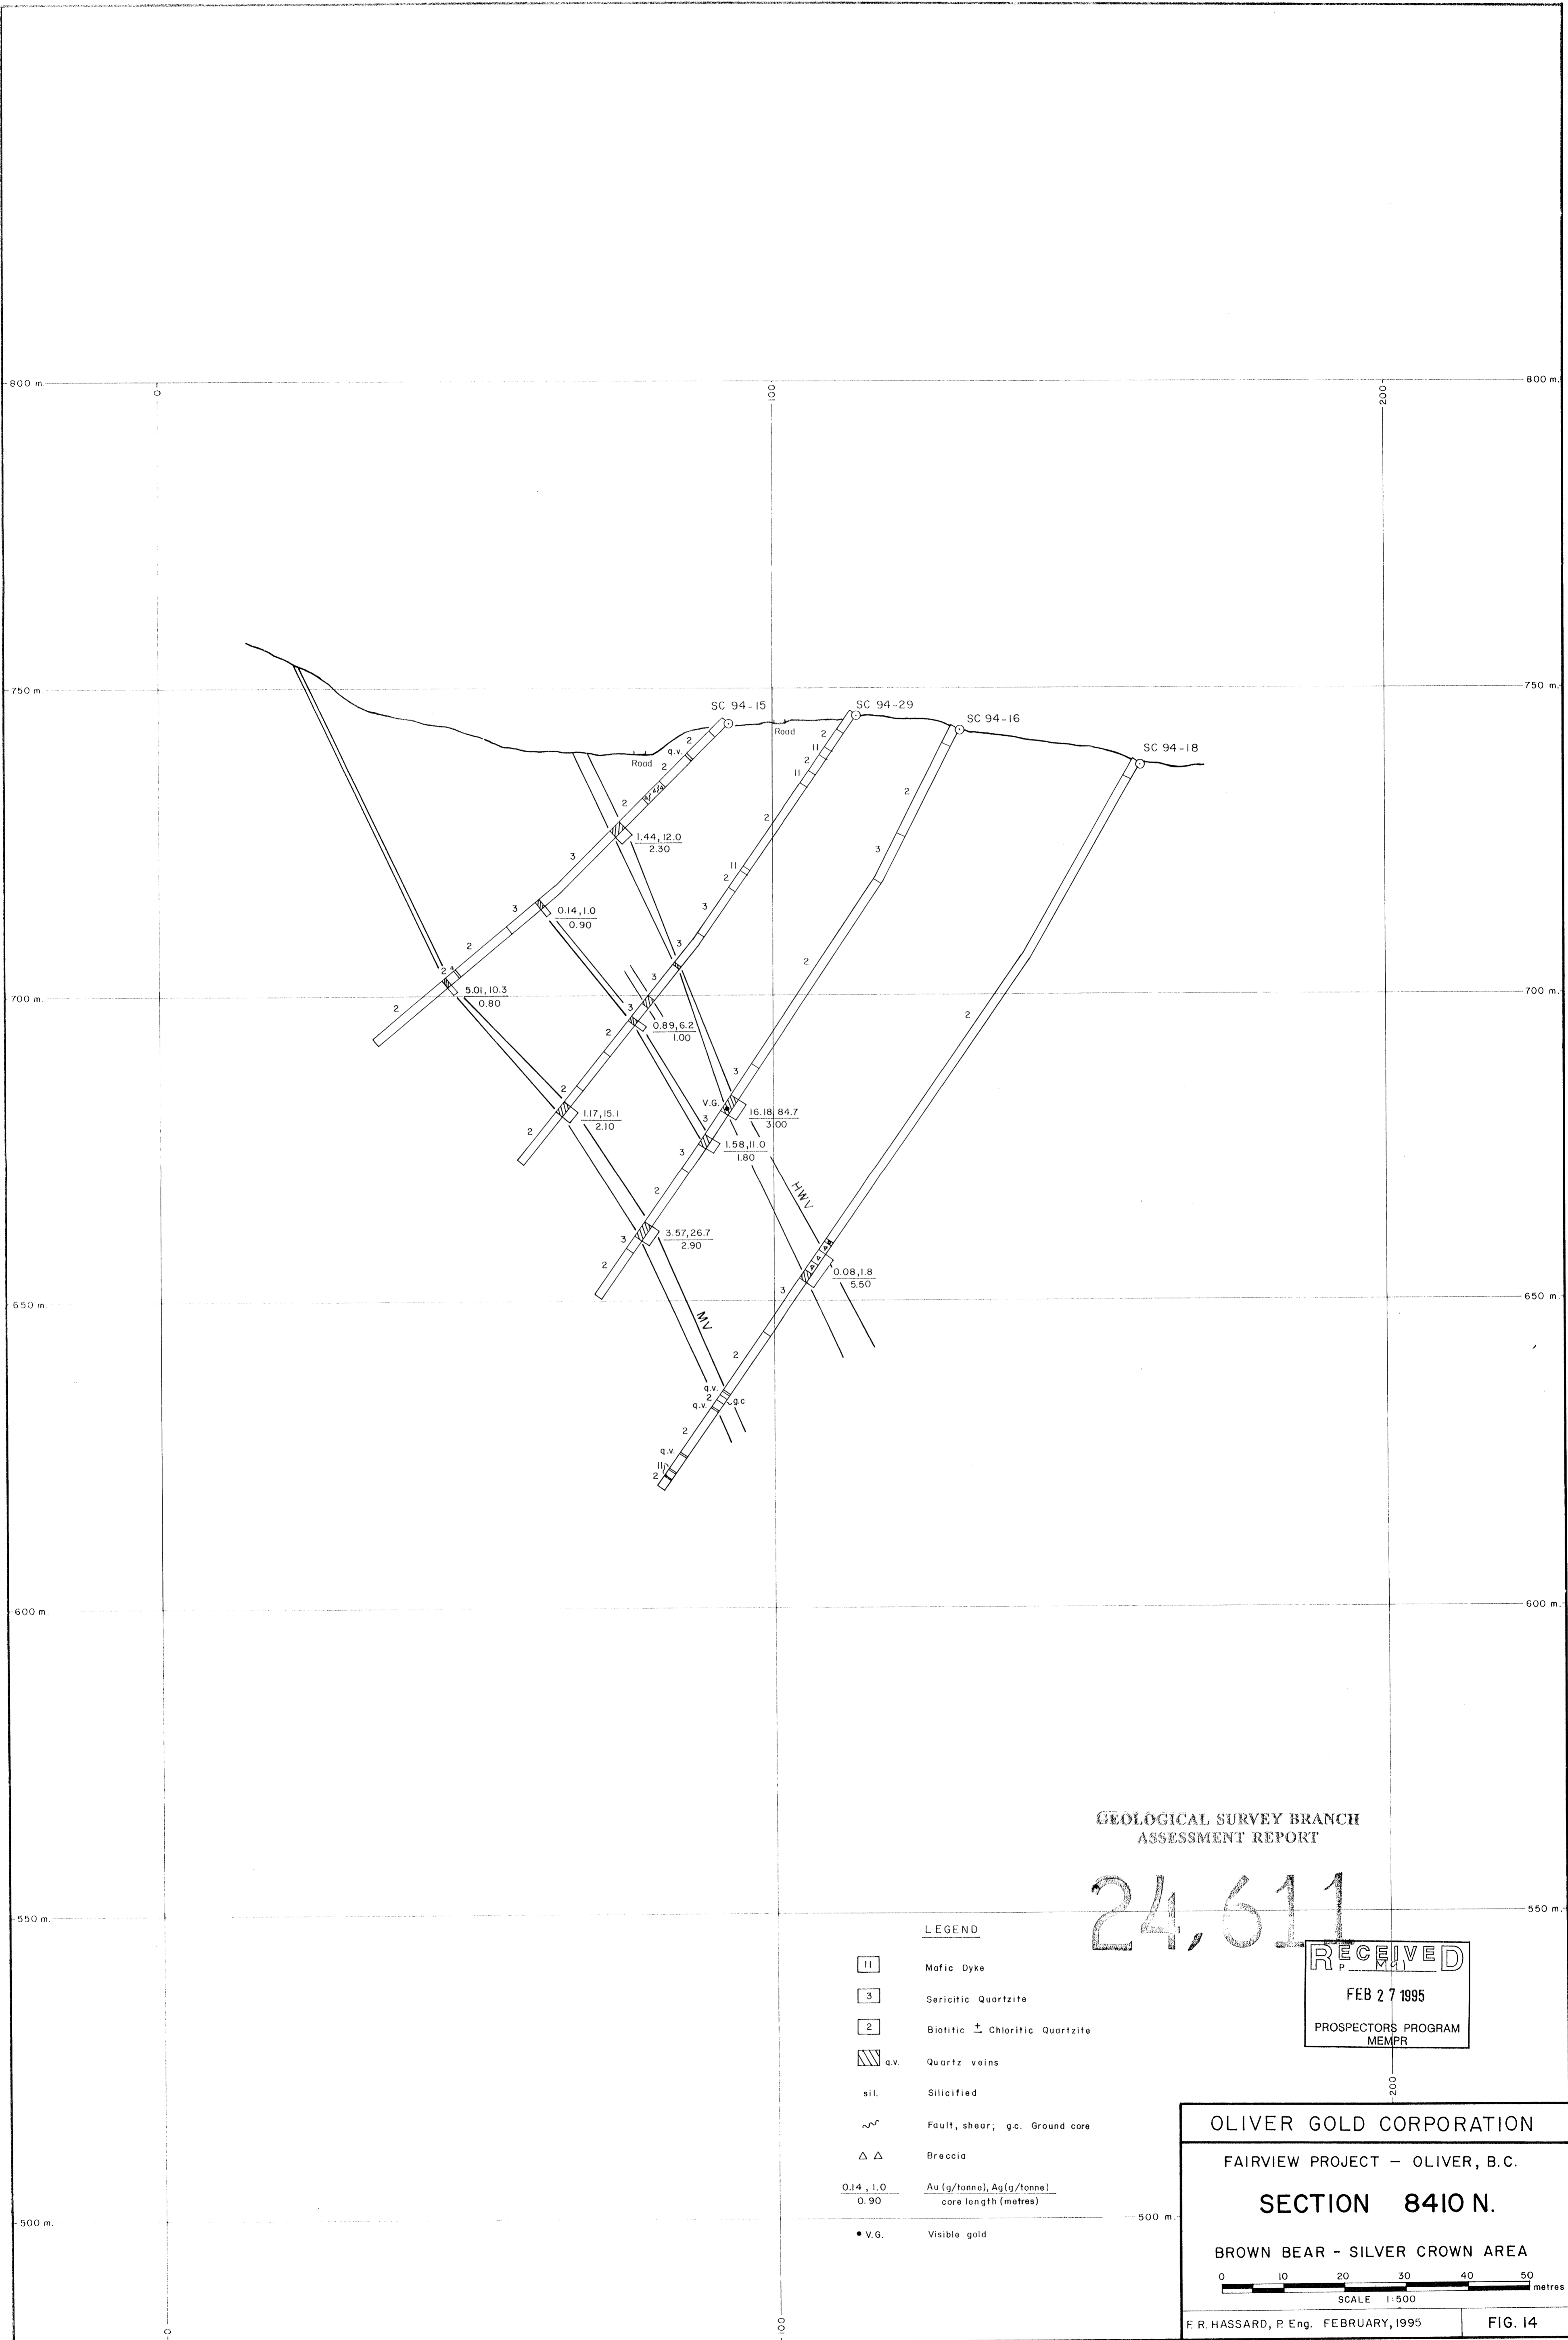

GEOLOGICAL SURVEY BRANCH
ASSESSMENT REPORT

24,611

RECEIVED
FEB 27 1995
PROSPECTORS PROGRAM
MEMPR

LEGEND


- 11 Mafic Dyke
- 3 Sericitic Quartzite
- 2 Biotitic ± Chloritic Quartzite
- q.v. Quartz veins
- sil. Silicified
- ~ Fault, shear; g.c. Ground core
- △ △ Breccia
- 0.14, 1.0 / 0.90 Au (g/tonne), Ag (g/tonne) / core length (metres)
- V.G. Visible gold

OLIVER GOLD CORPORATION
FAIRVIEW PROJECT - OLIVER, B.C.
SECTION 8410 N.
BROWN BEAR - SILVER CROWN AREA

0 10 20 30 40 50 metres
SCALE 1:500

F. R. HASSARD, P. Eng. FEBRUARY, 1995

FIG. 14

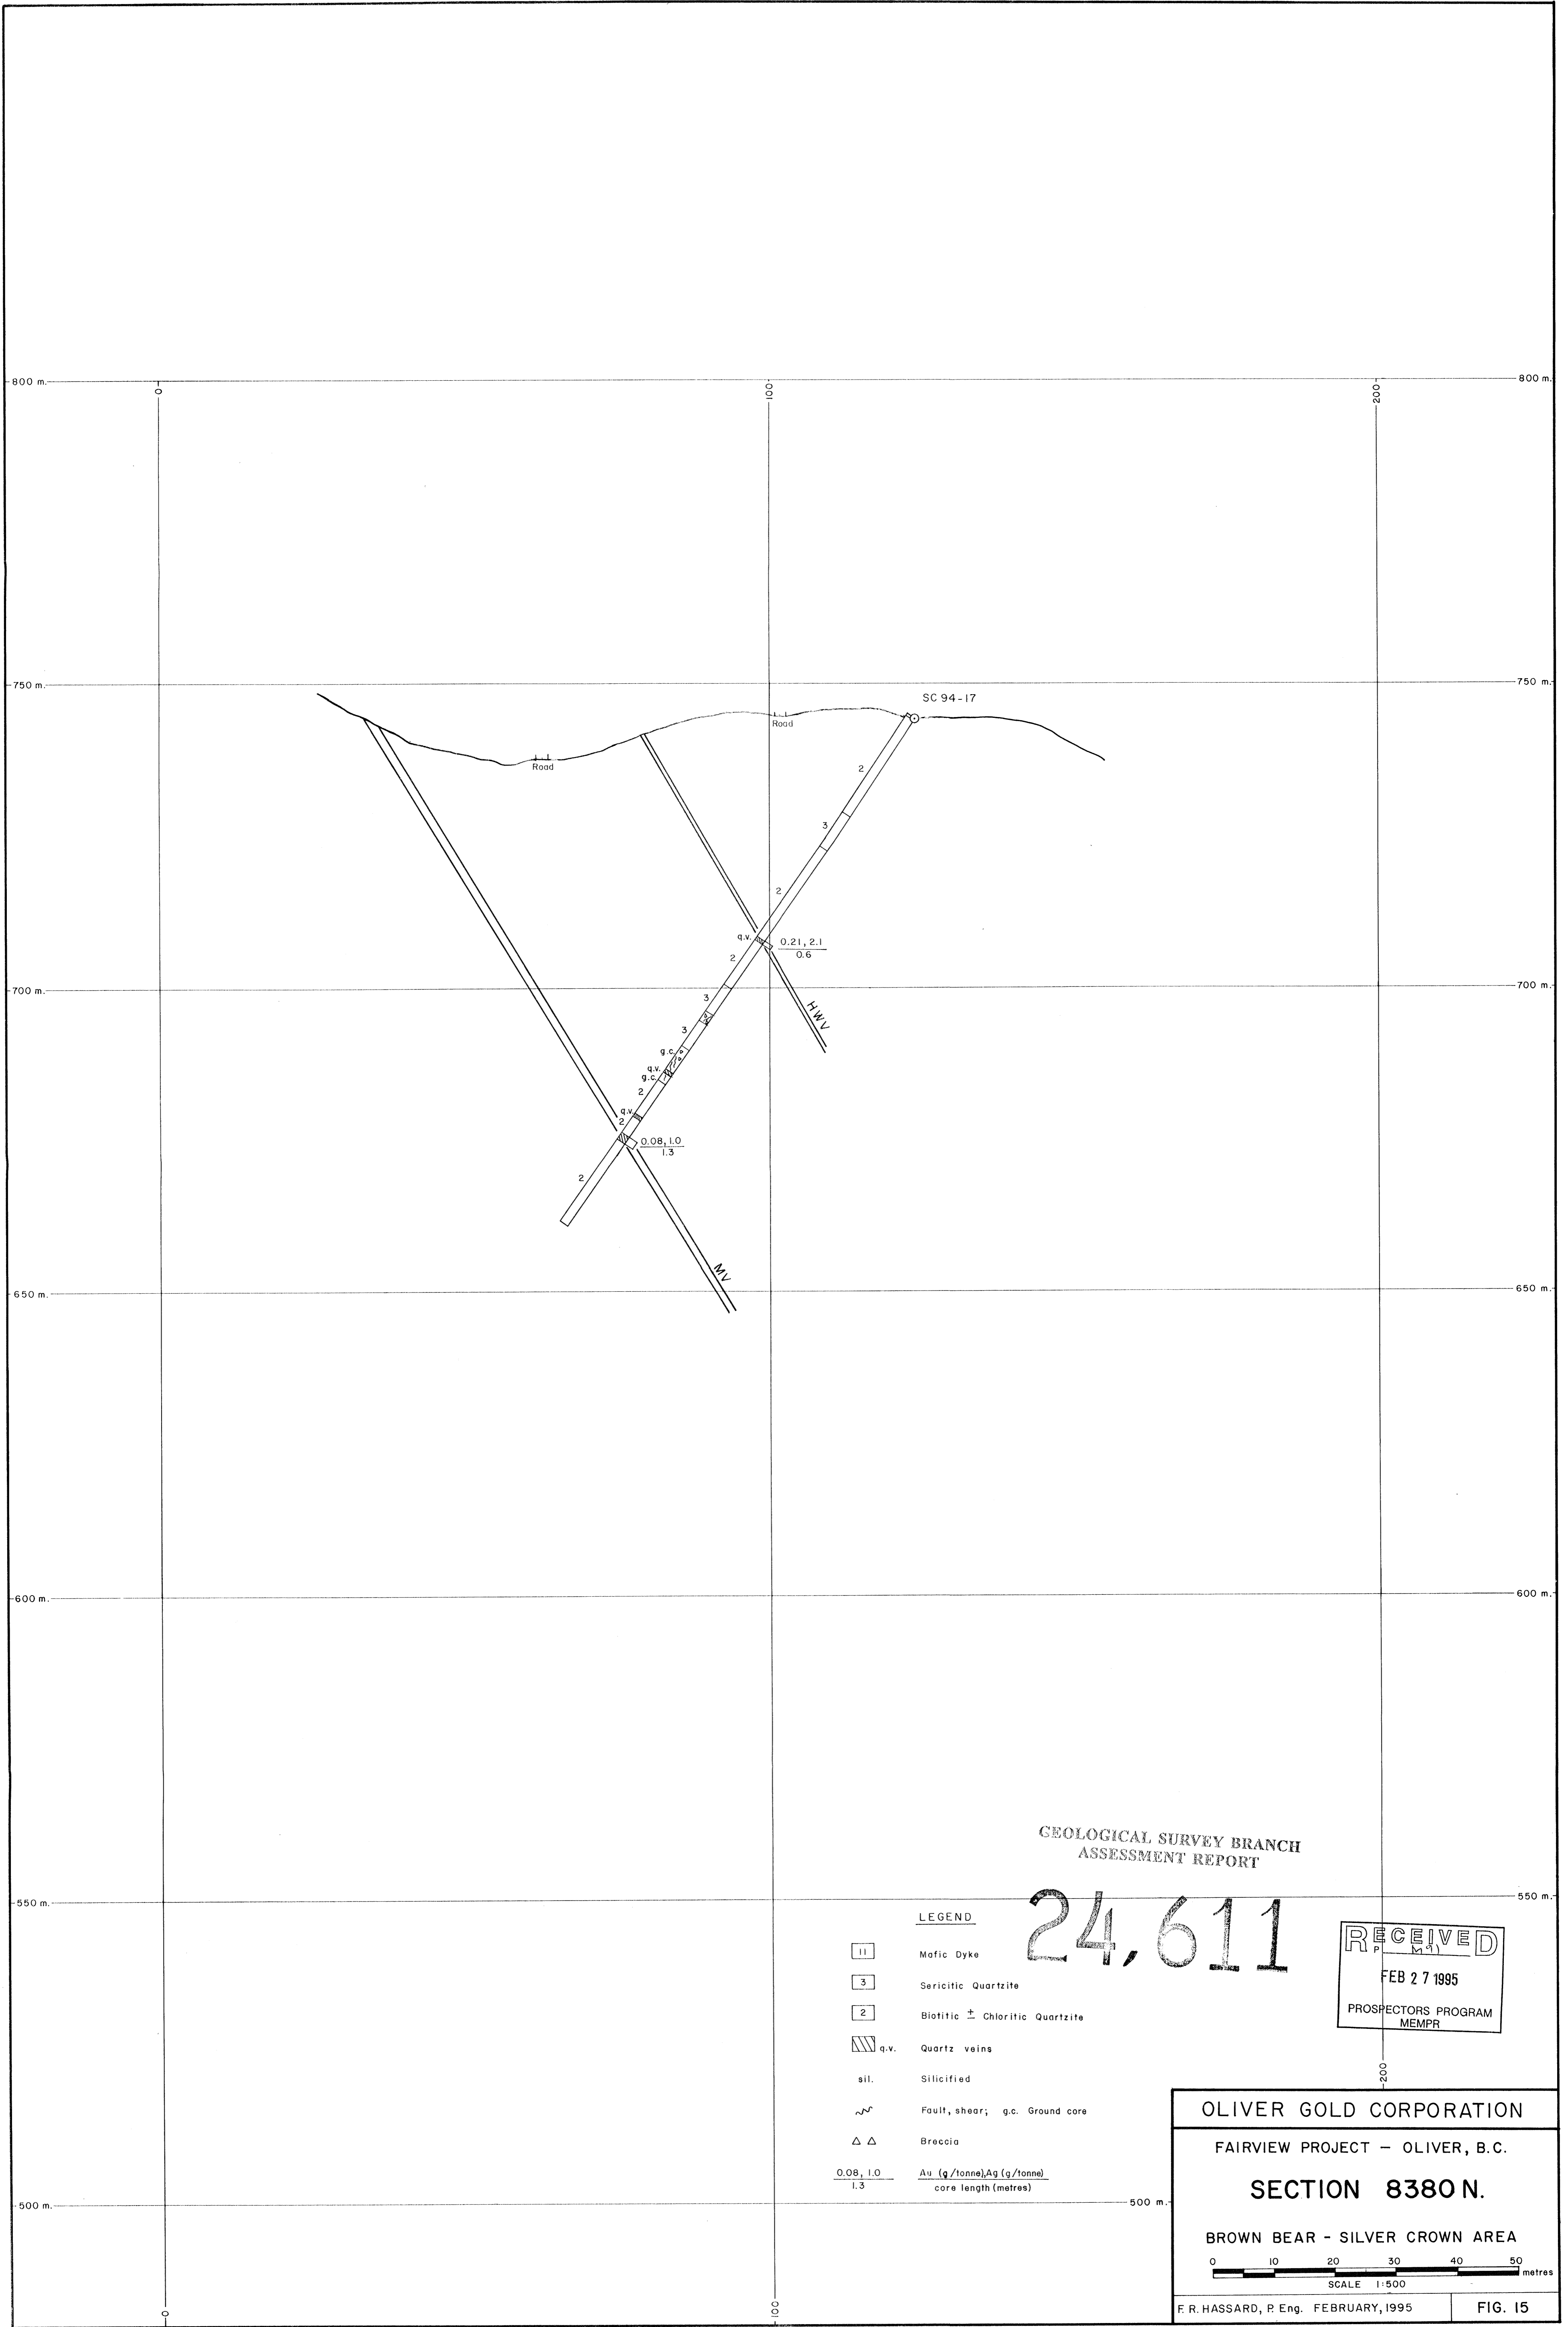

GEOLOGICAL SURVEY BRANCH
ASSESSMENT REPORT

24,611

- LEGEND**
- [1] Mafic Dyke
 - [3] Sericitic Quartzite
 - [2] Biotitic ± Chloritic Quartzite
 - ▨ q.v. Quartz veins
 - sil. Silicified
 - ~ Fault, shear; g.c. Ground core
 - Δ Δ Breccia
 - $\frac{0.08, 1.0}{1.3}$ $\frac{Au (g/tonne), Ag (g/tonne)}{core length (metres)}$


RECEIVED
FEB 27 1995
PROSPECTORS PROGRAM
MEMPR

OLIVER GOLD CORPORATION
FAIRVIEW PROJECT - OLIVER, B.C.
SECTION 8380 N.
BROWN BEAR - SILVER CROWN AREA

0 10 20 30 40 50 metres
SCALE 1:500

F. R. HASSARD, P. Eng. FEBRUARY, 1995

FIG. 15

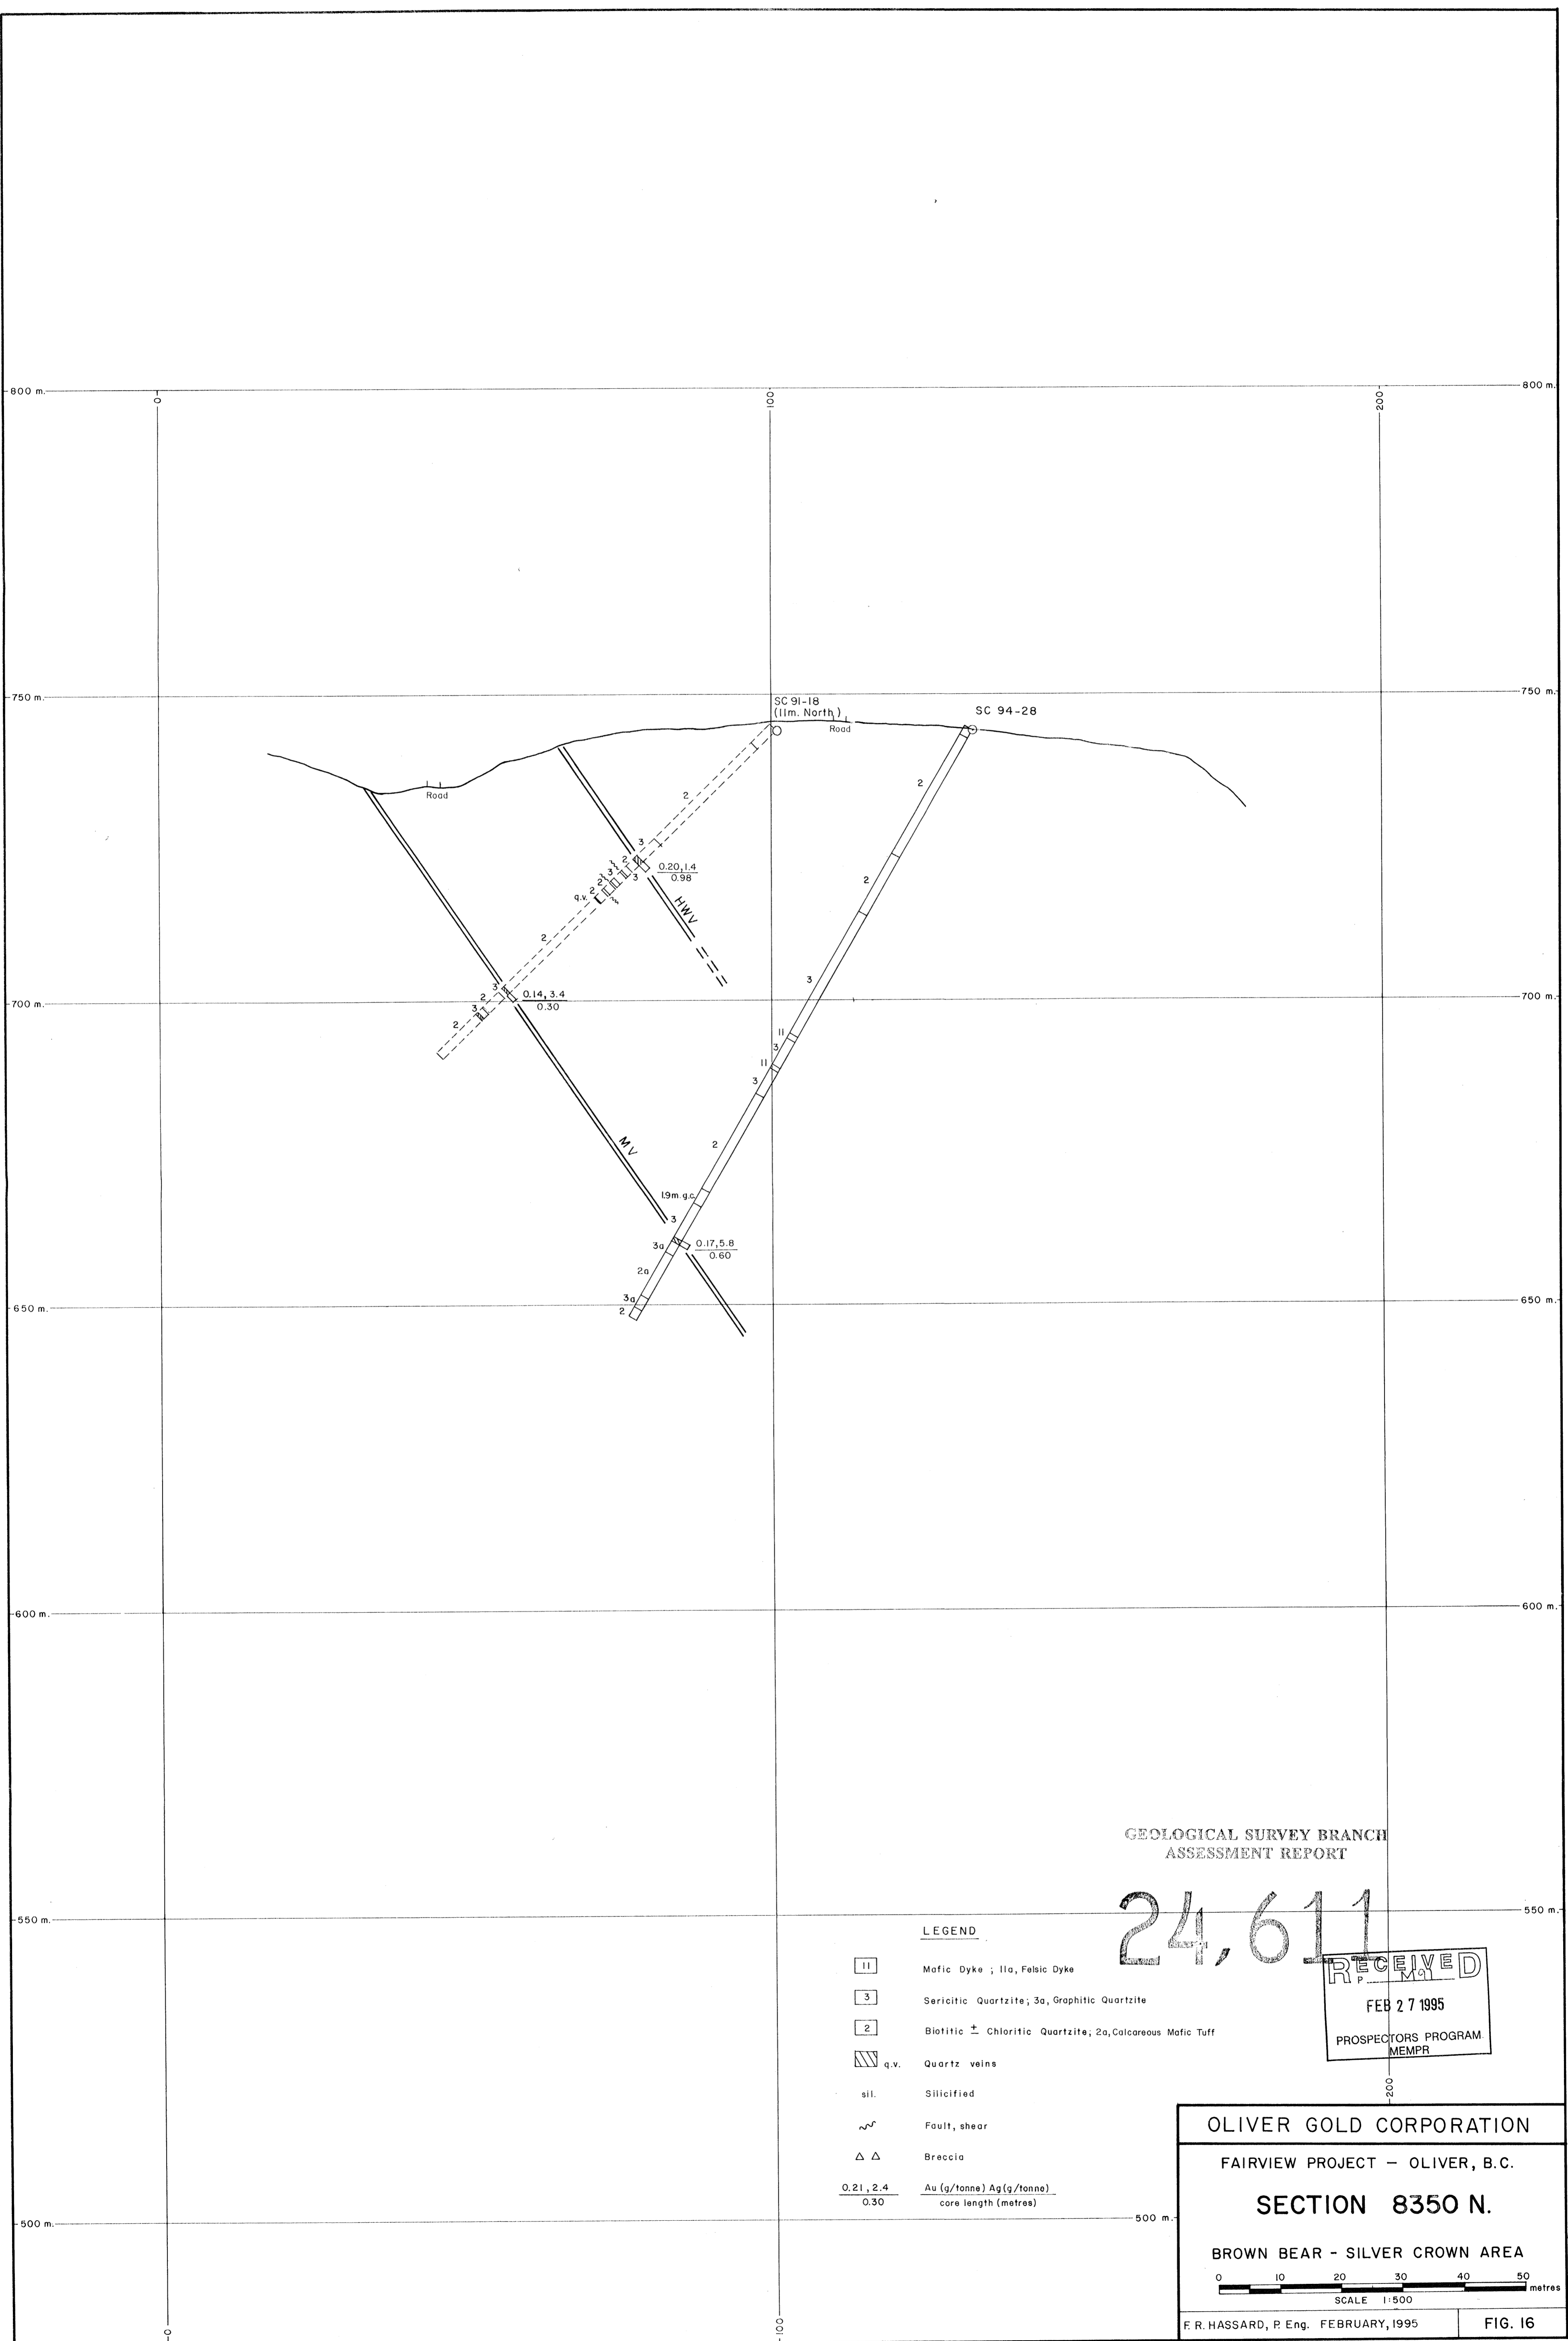

GEOLOGICAL SURVEY BRANCH
ASSESSMENT REPORT

24,611

RECEIVED
FEB 27 1995
PROSPECTORS PROGRAM
MEMPR

LEGEND


- 11 Mafic Dyke ; 11a, Felsic Dyke
- 3 Sericitic Quartzite; 3a, Graphitic Quartzite
- 2 Biotitic ± Chloritic Quartzite; 2a, Calcareous Mafic Tuff
- q.v. Quartz veins
- sil. Silicified
- ~ Fault, shear
- △ Breccia
- 0.21, 2.4 / 0.30 Au (g/tonne) Ag (g/tonne) / core length (metres)

OLIVER GOLD CORPORATION

FAIRVIEW PROJECT - OLIVER, B.C.

SECTION 8350 N.

BROWN BEAR - SILVER CROWN AREA



F. R. HASSARD, P. Eng. FEBRUARY, 1995

FIG. 16