

MUNICIPAL TITLES BRANCH
Rev 1.
MAR 20 2001
L.I.# _____
File _____
VANCOUVER, B.C.

NTS 92 B/12 W
LAT. - 48° 31' 00 N
LONG. - 123° 55' 00 W

**GEOLOGICAL AND GEOCHEMICAL
& DIAMOND DRILLING REPORT
on the VALENTINE CLAIM GROUP,
VALENTINE MTN, SOOKE, B.C.**

FOR:
BEAUPRE EXPLORATIONS LTD.,
108-3930 SHELBOURNE ST.,
VICTORIA, B.C. V8P 5P6

BY:
ANDRIS KIKAUKA, P.GEO.,
4-6 4901 EAST SOOKE ROAD,
SOOKE, B.C. V0S 1N0

MARCH 17, 2001 GEOLOGICAL SURVEY BRANCH
ASSIGNMENT REPORT MR. # _____
VICTORIA, B.C.

GOLD COMMISSIONER
RECEIVED and RECORDED
MAR 16 2001

26,517

TABLE OF CONTENTS AND LIST OF FIGURES

	PAGE NO.
1.0 INTRODUCTION	1
2.0 LOCATION, ACCESS AND PHYSIOGRAPHY	1
3.0 PROPERTY STATUS	1
4.0 AREA HISTORY	1
5.0 PROPERTY HISTORY AND GEOLOGY	2
6.0 GENERAL GEOLOGY	10
7.0 2000 FIELD PROGRAM	12
7.1 METHODS AND PROCEDURES	12
7.2 PROPERTY GEOLOGY & MINERALIZATION	13
7.3 DIAMOND BIT CORE DRILLING	14
7.4 BENCH TEST AND METALLURGICAL TESTING	14
7.5 PROSPECTING AND GRAB SAMPLING	15
8.0 DISCUSSION OF RESULTS	15
9.0 CONCLUSION AND RECOMMENDATION	16
10.0 REFERENCES	16
STATEMENT OF QUALIFICATIONS	17
ITEMIZED COST STATEMENT	18

LIST OF FIGURES

FIGURE 1 LOCATION MAP

FIGURE 2 CLAIM MAP

FIGURE 3 TOPOGRAPHY AND ACCESS ROADS, 'B' & 'C' VEIN, MILL AREA

FIGURE 4 GENERAL GEOLOGY

FIGURE 5 DRILL PAD LOCATIONS DDH 00-01 to 08, 'B' & 'C' VEIN

FIGURE 6 CROSS SECTION 9+00 E DDH 00-01, 04, & 05

FIGURE 7 CROSS SECTION 8+81.7 E, DDH 00-02

FIGURE 8 CROSS SECTION 8+63.4 E, DDH 00-03

FIGURE 9 CROSS SECTION 8+87.8 E, DDH 00-06

FIGURE 10 CROSS SECTION 9+18.7 E, DDH 00-07, 08

FIGURE 11 LOG DAM ZONE

APPENDIX A RECORD OF CLAIMS HELD BY BEAUPRE EXPL. LTD. & R. BEAUPRE

APPENDIX B FAIRBANK ENGINEERING LTD. ASSAY PLAN 'C' VEIN TRENCH

APPENDIX C GORD ALLEN LONGITUDINAL SECTION OF 'C' VEIN FOR ORE RESERVE CALCULATION

APPENDIX D DRILL LOGS WITH IMPERIAL DISTANCE MEASUREMENT

APPENDIX E GRAPHIC DRILL LOGS WITH METRIC DISTANCE MEASUREMENTS

APPENDIX F GEOCHEMICAL ANALYSIS AND ASSAY CERTIFICATES

1.0 INTRODUCTION

This report was prepared at the request of Beaupre Explorations Ltd. and consists of a compilation of geological fieldwork carried out between November 15, 2000 and Jan. 31, 2001 within the Valentine claim group. Fieldwork included diamond drilling, trenching, prospecting, geological mapping, and bulk sampling. The purpose of this report is to summarize geological data in order to evaluate the economic mineral potential within the claim group.

2.0 LOCATION, ACCESS & PHYSIOGRAPHY

The property is located 49 km. WNW of Victoria, and 19 km. N of Sooke on SW Vancouver Island (Fig.1 & 2). A network of logging roads, owned by Western Forest Products, access about 50% of the claims. A small portion of the logging roads have steep grades which require four-wheel drive. The main logging road access has weekday travel restrictions during the period 07:00 to 17:00 hours. The area gets occasional heavy rain washouts in the autumn, fire closures in the summer and snow at higher elevations in the winter. Relatively mild coastal climate allows year round fieldwork to be carried out.

The property is part of the Insular Mountains which formed as a result of crustal thickening and subsequent mature dissection of a Tertiary erosion surface of relatively low relief, now expressed as fault controlled valleys and fault-line scarps forming monadnock-like plateaus (Grove,E.W.,1990). The terrain is mountainous and rugged between 370-800 meters elevation (the lower levels of the claim group). Plateaus are developed on the ridge tops at elevations >800 meters above sea level. Quaternary ice advances from the north and west has deposited a 1-5 meter depth of till throughout the region.

3.0 PROPERTY STATUS (Appendix A)

The Valentine property consists of 58 claims (241 units=6,025 Ha) registered to Beaupre Explorations Ltd. and 21 claims (21 units=525 Ha) which are registered to Robert Charles Beaupre. Refer to Appendix A for a complete mineral title search of all of the claims from the Ministry of Energy and Mines website (see Appendix A). All of the 79 claims (262 units=6,550 Ha) have been grouped and have a common anniversary date of February 14. The Blaze 1 claim has a new expiry year of 2004, the Blaze 2-3, BPEX 1,2,4-7,12, & Doran 2,5 have an expiry year of 2003, and the other claims have been extended to an expiry year of 2002.

4.0 AREA HISTORY

Placer gold was discovered in the 1860's in sand and gravel alluvium along the San Juan, Leech, Jordan, Sombrio and Loss Creek drainage basins. Leech River was hydraulic mined intermittently until 1941. Nuggets up to 1 ounce and a total production of 10,000-20,000 ounces were sluiced from gravel/bedrock contacts along riverside bars.

Base and precious metal lode deposits in Southern Vancouver Island consist of massive sulphides, skarns, quartz veins and shears. Cu-Pb-Zn-Ag-Au massive sulphides occur near Mt. Sicker. Past producers in this area include Lenora, Tyee, Richard III, and Lara (which has published reserves of 529,000 tonnes grading 1.11% Cu, 1.22% Pb, 5.87% Zn, 4.73 g/t Au and 100.1 g/t Ag). Magnetite-chalcopyrite skarns in the Cowichan Lake area have produced in excess of 15 million pounds of copper and 75,000 ounces of silver. Shear zone copper deposits occur near the mouth of the Jordan R. where the Sunloch-Gabbro property is located. Past production includes several million pounds of Cu as well as minor silver and gold. The adjacent prospect known as the Sunro shear contains probable reserves of 1.47 million tonnes @ 1.43% Cu.

5.0 VALENTINE MOUNTAIN HISTORY AND GEOLOGY

Gold bearing quartz and/or sulphide zones have been the focus of attention on Valentine Mountain. A summary of previous work (which is mostly situated on Blaze 1,2 claims) is outlined as follows:

1. Gold bearing quartz is hosted in mixed schist/gneiss (i.e. metapelites/metasandstones). Amphibolite units are key stratigraphic horizons and outline major structures, and host gold bearing quartz in the area of the "Discovery Zone" (3 km. west of RB claims). A weakly altered, E-W trending, steeply dipping, laterally continuous, 50-200 m. thick amphibolite unit is in close proximity (about 5-50 m.) to the main series of gold-quartz veins. A total of 3 gold-quartz veins were defined by drill intercepts as follows:

"C" vein zone: Located parallel and 10-15 m. south of the "36" (aka "B" vein), the "C" vein consists of white to grey quartz, trace amounts of pyrrhotite, marcasite and native gold hosted in mixed gneiss and schist. DDH 82-6 intersected the "C" vein at 36.0-36.5 m. depth and returned 7.550 opt Au across 0.5 m. Several other holes drilled nearby (i.e. 82-3,7,7A,5,5A,6A) intersected the "C" vein with assay values up to 0.174 opt Au across 0.3 m.

"D" vein zone: Parallel and 50 m. north of the "C" vein is the "D" vein, which is localized along a fault zone along an amphibolite/gneiss contact. This vein was intersected by DDH 82-6A, 6, 5, & 21 with values up to 0.063 opt Au across 1.3 m., which was recorded in the drill hole furthest west, and appears that the vein improves westward along strike.

"A" vein zone: The depth continuity of the "A" vein was tested by DDH 82-15. At 150.4-151.3 m. (0.9 m. wide) and at 154.6-155.1 m. (0.5 m. wide), two veins were intersected that returned 0.042 and 0.098 opt Au respectively.

2) The "36" gold-quartz vein trench gave the following values:

DISTANCE	LOCATION	WIDTH	OPT Ag	OPT Au
2 m.	footwall	.46 m.	.07	.41
2 m.	vein	.17 m.	3.85	34.950
2 m.	hangingwall	.61 m.	.16	.852
10 m.	footwall	.36 m.	.56	.005
10 m.	vein	.03 m.	2.27	33.200
10 m.	hangingwall	.37 m.	.79	3.845
20 m.	footwall	.46 m.	.10	.142
20 m.	vein	.03 m.	.03	.003
20 m.	hangingwall	.50 m.	.02	.090
30 m.	footwall	.48 m.	.01	.010
30 m.	vein	.13 m.	.12	.328
30 m.	hangingwall	.37 m.	.10	.003

- Only 1 out of 13 drill holes (DDH #82-6) gave results (7.550 opt Au over 1.6 ft. or 0.5 m.) which compared to the multi-ounce assays returned from the high grade section of the "36" vein trench.
- The main reason for erratic results appears to be structural, i.e. free gold occurs in scattered pockets in the quartz veins, and in fractures and on shear planes in the adjacent wall rocks (Grove, 1984).

1. A bulk sample was shipped to Trail, B.C. (1983) giving the following results:

ANALYZED FOR:	SAMPLE # 1 (223 lbs.)	SAMPLE # 2 (296 lbs.)
	FINES from 5 tons sluiced	GOLD-QUARTZ grab vein & wall rock
GOLD	4.82 OPT	18.44 OPT
SILVER	0.60 OPT	1.25 OPT
SILICA	66.9%	89.4%

- Gold bearing quartz mineralogy includes crystalline arsenopyrite, marcasite, rare chalcopyrite, sphalerite, galena and ilmenite.
- Alteration within the 50-200 m. thick amphibolite unit adjacent to the "Discovery Zone" consists of : extensive quartz, calcite and gypsum veining, spotty to vein-like K-spar zoning, tourmalinization, epidotization, biotitization of hornblende, and magnetite development (Grove, 1984).
- Spatial relation of gold-quartz and extensive alteration suggest that the amphibolite unit is significant in the localization of gold ore.

5. Drill results reflect structure and give a "hit and miss" account of gold grades due to its scattered distribution as streaks, pockets and fracture infillings.

The 1985 Falconbridge mapping and trenching program identified the following geological features present in the "Discovery Zone":

1. The "36" and "A" vein gold-quartz systems trend at azimuth 068 degrees, dipping 70 degrees south.
2. There are numerous 090 trending, steep S dipping dextral strike-slip faults; offset by later dextral and sinistral strike slip micro-faults (several cm. displacement). Gold-quartz veins appear to have emplaced in between the macro and micro faulting events.
3. Gold grades of the main quartz vein and adjacent wall rock increase where there are zones of increased cross and/or diagonal faulting and fracturing
4. Calculation of weighted averages of vein and wall rock from the "A" trench returned a value of 0.094 opt Au over 1.38 m. along a strike length of 11.0 m.
5. Arithmetic averages of quartz vein from the "A" trench gave 0.959 opt Au and wall rock assays averaged 0.028 opt Au.
6. Biotite gneiss (metasandstone) is the dominant host lithology for gold-quartz veins in the "Discovery Zone". Carbonaceous andalusite-staurolite-garnet-biotite schist (metapelite) forms about 15% of the host lithology for the gold-quartz veins and occurs as narrow, 1-5.0 m. wide, E-W trending bands within the more massive biotite gneiss.
7. Samples identified as carrying visible gold returned assays of 0.001-0.013 opt Au. These samples included severe dilution from non-mineralized wall rock which would partially explain the low values. The other explanation is that the assay lab did not effectively metallic screen the entire sample to recover the observed native gold.

Bondar-Clegg treated a 42.1 kg. (92.8 lbs.) sample from the trench and obtained 8.74 grams Au and 0.46 grams Ag. The grade of this sample is 13.362 opt Au and 0.70 opt Ag.

In 1987-88, Valentine Gold established a bulk sample pilot mill and cored 43 diamond drill holes, with the following significant results:

"C" Vein zone:

Depth extension of the "C" vein (located 10-15 m. south of and parallel to the "36" vein), defined by a total of 10 drill intercepts are projected on longitudinal section by Gord Allen, outlined an ore reserve calculation of 33,795 tons of 0.429 opt Au (based on a 1.2 m. width) from the "C" vein. The "C" vein is located parallel to and 25-35 m. south of a 100 m. thick, steep south dipping altered amphibolite unit.

"D" vein zone: The "D" vein is located along the south contact of the altered amphibolite unit. This vein has an inferred strike length of 500 meters, but no ore reserves have been calculated due to grades which average less than 0.100 opt Au across 1.0 m. in the drill intercepts. The main feature of the "D" vein is a) amphibolite contact and b) fault-bound affinity. The "D" vein fault has led to poor recovery and consequent loss of fines as core drills cut this zone.

"E" vein zone:

The "E" vein was discovered by drilling towards a well defined Au soil anomaly 100 m. north of the "C" vein and 70 m. north of the "D" vein. The "E" vein is hosted by altered amphibolite, and is in close proximity to the gneiss/schist contact (10-40 m. to the north) and to a 2 m. wide, cross-cutting, (unit 5) quartz diorite dyke. DDH 87-14 recorded 0.226 opt Au across a 0.3 m. wide fault zone (@ 49.1-49.4 m.) and 0.033 opt Au across 1.0 m. (@ 78.0-79.0 m.), suggesting the presence of two parallel vein zones.

"A" vein zone:

The "A" vein was intercepted by DDH 87-3 returning 0.046 opt Au across 0.6 m. in a fault zone (@28.5-29.1 m.). The "A" vein is located 20 m. south of the altered amphibolite contact, thus there is some speculation that it is the continuation of the "D" vein because if we follow the zone west to 87-4,5 (0.136 opt Au over 1.0 m. and 0.031 opt Au across 0.9 m. respectively), these intercepts align with a fault zone adjacent to the altered amphibolite, characteristic of the "D" vein.

The results from drilling in the "Discovery Zone" resulted in an ore reserve calculation on the "C" vein zone:

CELL #	HOLE #	AREA m2	TONNAGE @1.2 m.	opt Au 1.2 m.wide	Ozs. Au
1	87-11	1054	3630	1.580	5735
2	88-16	996	3430	0.087	298
3	88-18	1550	5338	0.001	5
4	88-17	1454	5008	0.041	205
5	82-3	748	2576	0.019	49
6	82-6A	530	1825	0.149	272
7	82-6	530	1825	3.080	7393
8	87-22	980	3375	0.033	111
9	88-14	1185	4081	0.031	127
10	88-15	619	2132	0.145	309
Total tonnage= 33,795				Total ounces Au= 14,504	
Calculated grade= 0.429 opt Au				(see Appendix C)	

In 1988, Vancouver Petrographics Ltd. (Dr. John Payne, Dr Jeff Harris, & Wendy Sisson) prepared detailed reports on core and trench samples taken from gold bearing quartz/sulphide zones located 2.5 km. east-southeast of Valentine Mountain. A summary of their work is listed below:

1. The main rock types which host ore in the vicinity of the "Discovery Zone" trenches are a) metasandstone, b) metasiltstone, c) metamudstone. Less abundant host rocks include garnet-bearing schist and a mafic volcanic rock altered to chlorite-carbonate-epidote-actinolite.

- Several 1-3 m. wide granodiorite/quartz diorite dykes/sills cut the above sequence.
2. Regional deformation resulted in a series of SE trending folds with steeply dipping axial planes and moderately ESE plunging fold axes. Strongly folded, finely banded argillitic schist is crosscut at a high angle by quartz veins up to 10 cm. across. These veins are folded moderately to tightly about axes which may be coaxial to those which had already deformed the schist host rock. This suggests that two pulses of deformation occurred in the same stress field, and were separated by a tensional event during which quartz veins were introduced.
 3. Rocks from the "Braiteach Zone" are less deformed, and contain less interbedded argillaceous siltstone/mudstone than the "Discovery Zone".
 4. Early quartz veins are distended and smeared out, being locally obliterated in part. Less deformed quartz veins may represent later veins which represent tensional dilation that crosscuts the regional trend of foliation at a small angle.
 5. The "Discovery Zone" gold bearing veins contain quartz which has deformed and partly recrystallized to much finer aggregates, with inclusions of quartz with abundant fine grained pyrite and/or pyrrhotite along grain boundaries. Native gold occurs in later, discontinuous veinlets and replacement patches, whose emplacement is moderately controlled by grain borders of deformed quartz. Locally, native gold (and pyrrhotite) occurs in tiny tiny inclusions in coarse grained arsenopyrite.
 6. Paragenetic assemblages suggest that during metamorphism, native gold and arsenopyrite were concentrated into shear zones (preferentially in fold closures), and in part into quartz veins formed during early stages of deformation. The presence of K-spar envelopes and euhedral tourmaline suggests a component of hydrothermal contribution to Au-As bearing mineralization. At a later stage, further quartz veins formed, and gold migrated into some of these, possibly near the end of the deformational event.

Noranda Exploration Ltd. (1989), performed work on the area of the West Leech claims as part of a geological, geochemical, geophysical and diamond drilling program that covered an area 3-5 km. east and west of Valentine Mountain. A summary of Noranda's work is given as follows:

1. Unit 2 gneiss (metasandstone) is divided into 2 sub-units: 2a) meta-greywacke has a better developed schistosity and higher % of lithic fragments than 2b and is generally darker coloured, 2b) massive metasandstone light to dark grey colour with minor schistosity with 5% disseminated biotite. Unit 2b is very hard to break because it has been partially recrystallized.
2. Unit 1 schist (metapelite) is divided into 5 sub-units: 1a) phyllite, extremely fine grained and fissile, with abundant sericite and minor biotite on cleavage surfaces as a result of retrograde metamorphism related to movement along proximal faults. 1b) biotite schist, medium grey to black colour, quartz and biotite form light and dark bands 1-3 mm wide, garnet and/or andalusite/staurolite porphyroblasts are often observed within the biotite schist. 1c) Biotite-garnet schist, similar to 2b with the addition of 1-10 cm. reddish brown, euhedral garnet crystals. 1d) Biotite-garnet-staurolite schist, similar to 1c with the addition of euhedral staurolite commonly cruxiform. 1e) Biotite-garnet-staurolite-andalusite schist, similar to 1d

- with addition of 1-8 cm., pink andalusite porphyroblasts.
3. Cataclastic textures observed in unit 1 schist consist of angular quartz fragments that have been deformed and flattened in the direction paralleling schistosity as a result of mechanical forces caused by proximal faults and/or overthrusts.
 4. Unit 5 Eocene intrusives consist of quartz diorite which occurs as a 2.8 km. long X 0.1-0.6 km. wide sill feature that widens out in Walker Creek. This quartz diorite has numerous 1-3 m. wide aplite sills with localized 1-3 mm wide orange-red colour, euhedral garnets.
 5. Unit 6 pegmatite is leucocratic with calcic feldspar, sericite, quartz and localized tourmaline crystals up to 10 cm. in length. Pegmatite dykes and sills range from 0.1-1.5 m. width and occur in the Walker Creek area.
 6. 1-5 cm. wide parasitic "S" and "Z" folds were observed in schist layers and quartz veinlets, which serve as a guide to direction of fold hinges and indicate a major E-W trending, gentle east plunging anticline along the axis of Valentine Mountain Ridge.
 7. Quartz veins occur throughout all rock units mapped and vary from 0.05 to 2.0 m. width. They are generally milky white "bull" quartz with occasional subhedral crystals. Limonite is frequently observed, minor fine grained pyrite and lesser pyrrhotite occurs as fracture coatings in quartz. Arsenopyrite crystals were observed in quartz veins and wall rock. There appears to be an association of arsenopyrite and gold bearing quartz veins.
 8. Gold bearing zones within the amphibolite are associated with pyrrhotite aggregates (forming 3% of total volume), however not all pyrrhotite zones contain gold mineralization.
 9. Quartz veins hosted in schist (metapelite) generally parallel well developed schistosity. In gneiss (metasandstone), quartz veins 0.05-0.1 m. wide cut sandstone beds at angles of 30-45 degrees, and bedding is at low angles to foliation.
 10. Variation in quartz veining between various lithologic units reflects the units themselves, i.e. quartz vein material is of metamorphic origin with relatively minor influence of hydrothermal activity. Phyllites contain the least quartz and metasiltstones contain the most quartz, with amphibolite and metasandstone containing relatively medium amounts of quartz.
 11. Gold bearing quartz veins are predominantly hosted by metasandstone. The "B" quartz veins are translucent to transparent and commonly light orange in colour and the "C" vein is generally grey black in colour. Gold mineralization occurs within the vein material as well as the adjacent wall rock.
 12. Magnetometer data shows a strong, narrow, 120 trending dipolar (high and low) feature east of L 18100 E. In the area of the "Discovery Zone" this feature appears as a broad mag high over the amphibolite unit (probably caused by increased magnetite and/or pyrrhotite) and an adjacent mag low to the north which may reflect massive metasandstone. West of L 17600 E, a similar, narrow magnetic response has a more subtle character. The pronounced background and source shift hints at a possible fold axis occurring on L 17600 E at stn. 20750 N (also observed by IP data).
 13. IP data from the west "Discovery Zone" indicates a chargeability/resistivity high and coincident Au soil geochem anomaly between L 20600 E/20087 N and L 19600 E/ 20137 N. Core drilling this target between L 19800 E and L 19900 E proved to be successful in identifying two gold bearing zones localized along the contact of mixed

- metapelite/metasandstone and altered amphibolite. DDH 89-24 intersected 2.301 opt Au across 0.3 m. @ 59.1-59.5 m.
14. IP data from "BN" and "Braiteach" zones identified a similar IP chargeability/resistivity high and coincident Au soil geochem anomaly between L 17150 E to L 18000 E located parallel and 50-125 m. north of the baseline.
15. "Braiteach Zone" DDH 89-20 and 89-21 were collared on the west projection of Au intercept 0.136 opt Au across 3.0 m. in DDH 88-12. DDH 89-20 cut 17.8 m. overburden, the following 99.1 m. cored through amphibolite with 5-7% quartz as stringers and veinlets with no significant Au values. Increased quartz, with 3-4% pyrite, pyrrhotite and chalcopyrite occur at 62.8-63.8 m. Fault breccia and gouge with 2-3% pyrite and pyrrhotite was cut at 76.5-77.8 m. An increase in biotite rich layers occurs at 77.8-84.4 m. with up to 4% disseminated pyrite, pyrrhotite and chalcopyrite. DDH 89-21 had 25 m. of overburden, followed by 86.1 m. of amphibolite. An increase in biotite rich layers with 4% disseminated pyrite, pyrrhotite and chalcopyrite occurs at 75.1-82.6 m. Fault gouge and shearing with 2-3% pyrite occurs at 93.5-94.7 m. and 103.3-109.0 m.
16. "Discovery West" DDH 89-22,23,24 were drilled to intersect an IP target of high chargeability and resistivity which coincides with anomalous Au geochem and is interpreted as being the west extension of the "C" and "D" vein systems. DDH 89-22 cut 3 quartz veins, the largest being 20 cm., with mineralization consisting of 10% pyrite and 1% pyrrhotite. The "D" vein system located 4 m. above the metasandstone/amphibolite contact returned 740 ppb Au over 1.5 m. Within the amphibolite at 148.3-149.3 m. there is a 1.0 m. interval with visible gold that returned 0.027 opt Au. DDH 89-23 cut two quartz veins, the largest being 0.35 m. wide with 1-2% pyrite and 1% pyrrhotite which are interpreted as the "C" vein system was intersected at 56.9-58.4 m. returning 0.040 opt Au across 1.5 m. width and the "D" vein at 106.5-108.0 m. assaying 0.028 opt Au across 1.5 m. DDH 89-24 cut 4 quartz veins, the largest being 0.41 m. wide, with 1-2% pyrite and less than 1% pyrrhotite. DDH 89-24 intersected 2.301 opt Au across 0.4 m. @ 59.1-59.5 m. depth. This intersection is situated 2.2 m. above the metasandstone/amphibolite contact and is interpreted as the "D" vein system. At 69.0-70.0 m. depth, DDH 89-24 cut a biotite rich layer with 0.5% euhedral garnet porphyryblasts, 1-2% pyrite and 1% pyrrhotite which returned assay values of 0.087 opt Au across 1.0 m. At a depth of 129 m., DDH 89-24 intersected a 5 m. wide band of 2-3% pyrrhotite blebs (with assay values up to 0.013 opt Au across 0.4 m.), and the projected IP chargeability high correlates with this mineral zone.
17. Detailed mapping of the "BN Zone" shows the gold-bearing quartz vein systems are predominantly hosted by gneiss (metasandstone, unit 2), typically with 10-20% biotite and exhibiting "woodgrain texture". There is some interbedded biotite-garnet-staurolite schist (unit 1) at L 17600 E/20935 N where there are 5-25 m. wide quartz vein swarms along the contacts of unit 1 & 2. At the southern edge of the Au soil anomaly is a massive, chlorite altered amphibolite (unit 3).

1. A total of 41 rock chip samples were taken with the following highlights:

SAMPLE #	Au ppb	As ppm	WIDTH m.
59655	5950	2219	0.03
58559	5530	3	0.05
59662	3960	1730	0.02
59660	3850	573	0.02

- 19) "Braiteach Zone" trench sampling is summarized as follows: a) Zone #1 outcrops in a road cut on J-6 logging road where specks of visible gold were found in limonitic, vuggy quartz hosted in a hydrothermal alteration zone within metasandstone. Out of 5 channel, 3 panel and 1 grab sample, the highest geochemical value returned was 390 ppb Au and 538 ppm As. b) Zone #2 is located 55 m. north of the baseline on L 16800 E where a 0.08 m. wide E-W trending quartz vein was channel sampled in 11 locations along the outcrop, returning a high value of 740 ppb Au, and 875 ppm As. c) Zone #3 is 80 m. WNW of zone #2 and consists of a main E-W trending, steep north dipping quartz vein with 10-20% quartz stringers 1 m. from the vein, which decrease with distance from the main vein. Results produced a high value of 150 ppb Au and 1063 ppm As. d) 8 chip samples from Zones #4-6 returned values up to 159 ppb Au and 25 ppm As.
1. Rock chip sampling on the Peg and Bo Claim Groups (Walker Creek area), returned 0.67% Cu across 0.2 m. and 0.28% Cu across 0.1 m.
 2. Recommendations for further work include exploration and development of low tonnage, high grade ores shoots along the 7 km. strike length which is known to host gold-bearing quartz vein systems.

1994- Fairbank Engineering Ltd performs detailed mapping of the 'C' vein trench at a scale of 1:250 (Appendix B). A total of 13 samples were taken ranging in width from 9-110 cm. Sample No. 6 returned a value of 30.20 g/t Au across a width of 7 cm.

1998- A geological and exploration evaluation of the Valentine Mountain Gold Property was carried out by Burgoyne Geological Inc.(Burgoyne, 98). The report concluded that the highest priority exploration targets include the areas 50-300 m east of and 200-600 m west of the mill site (Figure 3). The high priority areas include Discovery ("B" and "C" Veins) depth extension, Discovery West (Noranda DDH 89-24), and Log Dam (mag and Au in soil anomaly located approximately 300 m west of mill site).

6.0 GENERAL GEOLOGY (FIG. 4)

L.H. Fairchild (1979), completed a structural and metamorphic analysis of the Leech River Group in partial fulfillment of the requirements for a Masters degree at the University of Washington. Most of his work focused on the Valentine Mountain area. A point form summary of his study is listed below:

1. Leech River Group consist of greenschist to amphibolite facies gneiss and schist metamorphic rocks Their protolith rock types listed in order of abundance are: a-pelite (shale), b-sandstone, c-volcanic, d-chert, e-conglomerate.
1. Two Eocene deformational events, separated by a static period of unknown duration, consisted of fragmentation, rotation and regional shortening resulted in axial-plane cleavage, linear structures and coaxial mesoscopic parasitic folds about east-plunging fold axes.
2. Amphibolite facies metamorphism resulted in biotite-garnet and staurolite-andalusite successively introduced by continuous reaction, which extended from the end of the first phase of deformation into the second phase.
3. Greenschist facies metamorphism results in muscovite-chlorite-quartz assemblages.
4. San Juan, Clapp Ck. And Leech R. faults are E-W trending, steeply dipping, relatively straight zones of regional sub-parallel fault traces. The Leech R. fault is interpreted to be a left-lateral strike-slip fault zone active during the Eocene-Oligocene-Miocene.
5. In the Jordan R. valley southwest of Valentine Mountain, 10-50 m. wide coarse-grained biotite orthogneiss to granioritic sills and related pegmatite dykes are concordant with regional schistosity.
6. In both mesoscopic and macroscopic folds throughout the Leech R. Group, metasandstone and metavolcanic units behave competently and pelitic rocks, which typically filled-in between competent bodies, behaved in a more ductile fashion. This competency contrast indicates that buckling, rather than homogenous flattening or slip-folding, was the dominant mechanism of folding.
7. Isoclinal F1 structures are refolded by F2 resulting in cylindrical folds which are generally asymmetric-open in the north study area, and progressively symmetric-closed to the south.
8. Dominant foliation in the study area is steeply dipping, F2 axial planar.

Gay A. Wingert (1984), completed a B.Sc. thesis for U.B.C. entitled Structure and Metamorphism of the Valentine Mountain Area, SW Vancouver Island, B.C. Her study is summarized as follows:

1. The Leech R. Fm. underwent 2 stages of deformation and metamorphism which correlates with 2 stages of intrusion. Evidence for polymetamorphism is defined by distribution of staurolite and andalusite, indicating there was a primary metamorphic event which reached temperatures high enough to produce andalusite and a secondary metamorphic event of lower grade which only produced staurolite.
2. The second stage of metamorphism began prior to the second stage of deformation.

3. The final stages of igneous activity (presumed to have occurred in Late Eocene to Early Oligocene) coincide with dextral strike-slip movement along the Leech R. Fault. Retrograde alteration consists of staurolite & andalusite partially replaced by sericite-chlorite-quartz, garnets are crushed and altered to chlorite, and biotite and hornblende appears kinked and boudinaged. Late stage retrograde alteration is associated with late stage faulting and intrusive activity which produced dykes & sills, and gold-bearing quartz.
4. The axial trace of a regional E-W trending anticline fold axis is centered on Valentine Mountain.
5. Walker Creek is an axis for an E-W trending anticline fold axis

The B.C. Geological Survey Branch and the G.S.C. prepared a paper titled Andalusite in British Columbia- New Exploration Targets (Dr. G. Simandl, et.al., 1994)). There was a chapter of this paper devoted to the Leech River Area with specific reference to potential economic deposits within the subject property (Appendix A). A point form summary of this paper is given below:

1. Typical grades of primary "hard rock" andalusite ores vary from 7 to 20%. Typical production capacities of individual mines vary from 25,000 to 65,000 tonnes per year.
2. The coarser the crystals, the easier it is to upgrade the ore. Garnet and staurolite typically coexist with andalusite and where grades and textures permit, they are recovered as byproducts.
3. Most of the area east of Valentine Mountain contains andalusite strongly retrograded to either mica and staurolite or mica and chlorite. The retrograde alteration appears to be strongest in the "Discovery Zone"
4. The degree of retrograde alteration diminishes west of Jordan River where an E-W trend is especially interesting and may host zones of economic andalusite-garnet-staurolite.
5. There is a 6 m. wide zone of 7% andalusite bearing schist surrounded by a felsic intrusion.

The following legend is used to described rock types of the Leech River Group and younger intrusive rocks which underlie the West Leech claim group:

EOCENE AND YOUNGER? INTRUSIVE ROCKS

- 6 Pegmatite, Leucocratic dykes and sills
- 5 Quartz diorite, minor granodiorite, granite
- 5a Aplitic dykes and sills (leucocratic, fine grained)

TRIASSIC TO CRETACEOUS? LEECH R. GROUP METAMORPHIC ROCKS

- 4 Phyllite (finer grained and better cleaved than schist)
- 3 Amphibolite (metavolcanic)

3a Tuff
3b Flow
3c Pervasive chlorite alteration

2 Gneiss (metasandstone)
2a "Dirty"- greywacke
2b "Clean"- metaquartzite

1 Schist (metapelite)
1a Biotite schist
1b Biotite-garnet schist
1c Biotite-garnet-staurolite schist
1d Biotite-garnet-staurolite-andalusite schist

7.0 2000 FIELDWORK

7.1 METHODS AND PROCEDURES

A total of 182.73 meters of BQ core drilling (DDH 00-01 to DDH 00-08) was performed from 6 different pads (Figure 5). The core was logged (Appendix D for Imperial distances and Appendix E for metric distances) and marked for core splitting. A total of 81 core samples were bagged and sent to Bondar-Clegg, N. Vancouver for 30 element ICP and Au assay (Appendix F).

A grab sample labeled RW REEF C was taken from the Discovery Zone 'C' trench along a 10 cm wide ribbon quartz vein at the east edge of the trench (Figure 5). This sample was bagged and sent to Bondar-Clegg, N. Vancouver for 30 element ICP and Au assay (Appendix F).

A 1,000 kg sample of 'C' vein was taken for metallurgical testing (bench test) and shipped to Richmond, B.C. for dry processing by the KDS unit owned by First American Scientific Corp. and operated by Vancouver Blower. The 1,000 kg sample was shipped as two samples, and prior to shipping, the second (500 kg.) sample was homogenized, split and quartered resulting in 3 representative rock chip samples (No. 232251, 232252, and 232253) each of which weighed about 2 kg. The 3 rock chip samples were shipped to Bondar-Clegg for head grade analysis (Appendix F). For reasons of confidentiality, results from the bench test are not included in this report.

A panned sample of pulps was run through the First American Scientific Corp. KDS unit. A representative sample (No. V22664) of the concentrate was sent to Bondar-Clegg, N. Vancouver for Au and Ag assay (Appendix F).

A 2.0 kg. rock chip sample was taken across a width of 50 cm from a bedrock exposure located about 300 meters west of the mill site at the 'Log Dam' area (Figure 11). The sample was marked No. 22665, bagged and sent to Bondar-Clegg, N. Vancouver for 30 element ICP and Au assay (Appendix F).

7.2 PROPERTY GEOLOGY AND MINERALIZATION

The Valentine Property is underlain by the Leech River Group metasediments and metavolcanics. The following lithologies were recognized:

EOCENE AND OLDER (CATFACE INTRUSION)

- 6 Pegmatite, leucocratic with calcic feldspar.
- 5 Quartz diorite

TRIASSIC TO CRETACEOUS? LEECH R. GROUP METAMORPHIC ROCKS

- 3 Amphibolite (metavolcanic), 20-60% actinolite, 10-20% chlorite, 1-4% calcite as stretched vescicles
- 2 Biotite gneiss, (metasandstone, greywacke) weakly developed gneiss texture, locally feldspathic
- 1c Biotite-garnet-staurolite schist (metapelite), cruciform, euhedral porphyryblasts of staurolite, 1-4% almandine garnet
- 1b Biotite-garnet schist, 1-3% euhedral almandine garnet

The low grade metamorphism has produced abundant quartz veining which occurs as milky white to clear veins and veinlets forming 1-20% of the volume of bedrock. The gold bearing veins contain quartz which has deformed and partly recrystallized to much finer aggregates, with inclusions of quartz with abundant fine grained pyrite and/or pyrrhotite along grain boundaries. Native gold occurs in later, discontinuous veinlets and replacement patches, whose emplacement is moderately controlled by grain borders of deformed quartz. Locally, native gold (and pyrrhotite) occurs in tiny tiny inclusions in coarse grained arsenopyrite. Paragenetic assemblages suggest that during metamorphism, native gold and arsenopyrite were concentrated into shear zones (preferentially in fold closures), and in part into quartz veins formed during early stages of deformation. The presence of K-spar envelopes and euhedral tourmaline suggests a component of hydrothermal contribution to Au-As bearing mineralization. At a later stage, further quartz veins formed, and gold migrated into some of these, possibly near the end of the deformational event.

7.3 DIAMOND BIT CORE DRILLING (FIG. 6-10)

Core drilling was set up to intersect the known 'C' vein structure (which strikes 092 and dips 60-75 degrees south) at an oblique angle and to cut quartz veining that may be perpendicular to the known structure. The results of significant precious metal intercepts are listed as follows:

DDH	From	To	Width	Au OPT
00-03	34.0 ft	34.8 ft	0.8 ft	0.094
	10.37 m	10.61 m	0.24 m	
00-03	74.8 ft	79.8 ft	5.0 ft	0.116
	22.81	24.33 m	1.52 m	
00-06	13.2 ft	14.5 ft	1.3 ft	0.019
	4.03 m	4.42 m	0.39 m	

The presence of minor amounts of arsenopyrite as medium to coarse grained aggregates, are coincident with an increase in gold (Appendix E).

7.4 BENCH TEST AND METALLURGICAL SAMPLING

Approximately 1,000 kg of rock chips taken from the east end of the 'C' Vein trench, was split and quartered to extract three 2.0 kg samples which gave the following assay results:

Sample No.	Au OPT
232251	0.286
232252	0.319
232253	2.689

A panned concentrate of pulps run through the First American Scientific Corporation's KDS unit gave the following results:

Sample No.	Au OPT	Ag OPT
V22664	495.229	94.12

7.5 PROSPECTING AND GRAB SAMPLING (FIG. 5 & FIG. 11)

Two rock chip samples taken from the 'C' Vein and Log Dam area are summarized as follows:

Area	Sample No.	Width	Au OPT	Ag OPT
'C' Vein Trench, well developed ribbon quartz texture (Fig. 5)	RW REEF C	Grab	69.644	5.60
Log Dam Quartz Vein, abundant chlorite (Fig. 11)	22665	0.50 m	0.005	0.02

Sample RW REEF C was taken in from ribbon texture quartz with coarse grain arsenopyrite. Some visible gold was observed adjacent to sample RW REEF C. The visible gold occurs as 0.1-1.0 mm thick coatings and irregular masses. The pieces with visible gold were not analyzed, but kept for display purposes.

8.0 DISCUSSION OF RESULTS

Drill results indicate a scattered distribution of gold bearing quartz, suggesting that the higher grade gold values occur as streaks, pockets and/or fracture infillings along deformation zones. The style of gold bearing quartz/sulphide mineralization which occurs on the Valentine Mountain Property is a typical low-sulphidation mesothermal ribbon quartz-fissure vein system emplaced by a somewhat untypical Eocene intrusive complex. What makes the Eocene (Catface) intrusive unusual is the fact that the Mesozoic volcanic and sedimentary rocks of the Leech River Formation were metamorphosed by locally dynamic tectonics into a low temperature-medium pressure complex. The metamorphic host rock has resulted in ribbon texture recrystallized quartz being the dominant ore texture. It is possible that the emplacement of hydrothermal fluids was constrained by complex macro and micro fault displacements which has resulted in erratic distribution of gold values. 'Nugget effect' gold distribution is evident, for example, the value of 69.644 OPT Au obtained from a grab sample of the 'C' Vein (rock chip sample no. RW REEF C) had 2 drill holes pass within 10 m of the vein projection, and neither drill hole cut gold values similar to the grab samples, suggesting that sample RW REEF C is a structurally trapped pocket or lens of high grade gold.

9.0 CONCLUSION & RECOMMENDATION

Based on the results of rock chip samples, there is potential to host a gold deposit(s) on the Valentine Mountain Property. Further trenching, geological mapping, diamond drilling and prospecting in the area 600 m west and 250 m east of the mill site is recommended to locate additional gold bearing quartz/sulphide mineralization. Particular attention should be focused on minor flexures and/or cross faulting along the main east-west trending, steep south dipping quartz vein zones. The quartz/sulphide 'corridor of mineralization' that occurs adjacent to the Discovery and Log Dam area would be the most likely environment for further accumulations of quartz/sulphide mineralization.

If significant gold bearing quartz veins could be identified, then a phase 2 follow up program of trenching and diamond drilling would be recommended. Approximate budgets for the completion of phase 1 and 2 would be in the order of \$100,000 and \$150,000 respectively.


10.0 REFERENCES

- Allen, G. (1989): Valentine Mountain Property "C" Vein Ore Reserves, Beau Pre Expl. Ltd.
- Burgoyne, A.A., (1998): Geological and Exploration Evaluation Report on the Valentine Mountain Gold Property, Assessment Report for Beaupre Explorations Ltd.
- Fairchild, L.H. (1979): The Leech River Unit and Leech River Fault, Southern Vancouver Island, B.C.; M.Sc. Thesis, University of Washington.
- Fairchild, L.H. (1982): Structure, Petrology, and Tectonic History of the Leech River Complex, NW of Victoria, Vancouver Island; Can. Journal of Earth Sciences, Vol. 19, pages 1817-1835.
- Grove, E.W. (1981): Assessment Report, Blaze & BPEX Claims, for Beau Pre Explorations Ltd.
- Grove, E.W. (1982): Geological Report and Work Proposal on the Valentine Mountain Property for Beau Pre Explorations Ltd.
- Grove, E.W. (1984): Geological Report and Work Proposal on the Valentine Mountain Property for Beau Pre Explorations Ltd.
- Simandl, G.J., (1994): Andalusite in British Columbia-New Exploration Targets, B.C. Geological Survey Branch and G.S.C.
- Valentine Gold Corp. (1988): Valentine Mountain Project Report.
- Wingert, G.A. (1984): Structure and Metamorphism of the Valentine Mountain Area, SW Vancouver Island

I, Andris Kikauka, of 4901 East Sooke Rd., Sooke B.C., hereby certify that;

1. I am a graduate of Brock University, St. Catharines, Ont., with an Honours Bachelor of Science Degree in Geological Sciences, 1980.
2. I am a Fellow in good standing with the Geological Association of Canada.
3. I am registered in the Province of British Columbia as a Professional Geoscientist.
4. I have practised my profession for twenty years in precious and base metal exploration in the Cordillera of Western Canada, U.S.A., South America, and for three years in uranium exploration in the Canadian Shield.
5. The information, opinions, and recommendations in this report are based on fieldwork carried out in my presence on the subject properties.
6. I have no direct or indirect interest in the subject claims or the securities of Beaupre Explorations Ltd.
7. I consent to the use of this report in a Prospectus or Statement of Material Facts for the purpose of public or private financing.
8. It is believed that the information contained within this report is reliable. The author (A.A.Kikauka, P.Geo), does not guarantee accuracy. The use of this report or any part thereof, shall be at the user's risk.

Andris Kikauka, P. Geo.,



March 17, 2001

ITEMIZED COST STATEMENT- VALENTINE CLAIM GROUP,
NOVEMBER 15, 2000 to JANUARY 31, 2001
VICTORIA MINING DIVISION, NTS 92.B 12/W


FIELD CREW:

Andris Kikauka, Geologist 18 days	\$ 3,656.00
Simon Salmon, Geotechnician, 75 days	13,125.00
Robert Beaupre, Geotechnician, Manager 60 days	12,000.00
Wayne Walker, Geotechnician, 4 days	600.00
Tom Kirk, Geotechnician, 2 days	300.00
Bill Pfaffenberger, Geotechnician, 2 days	300.00

FIELD COSTS:

Core Drilling and Site Preparation, Neill's Mining	
182.73 m of core drilling (BQ)	18,255.00
87 rock samples, Au assay and 30 element ICP	2,912.50
Communication	550.00
Truck rental, 16 days	1,185.00
Report	802.50

Total= \$ 53,686.00

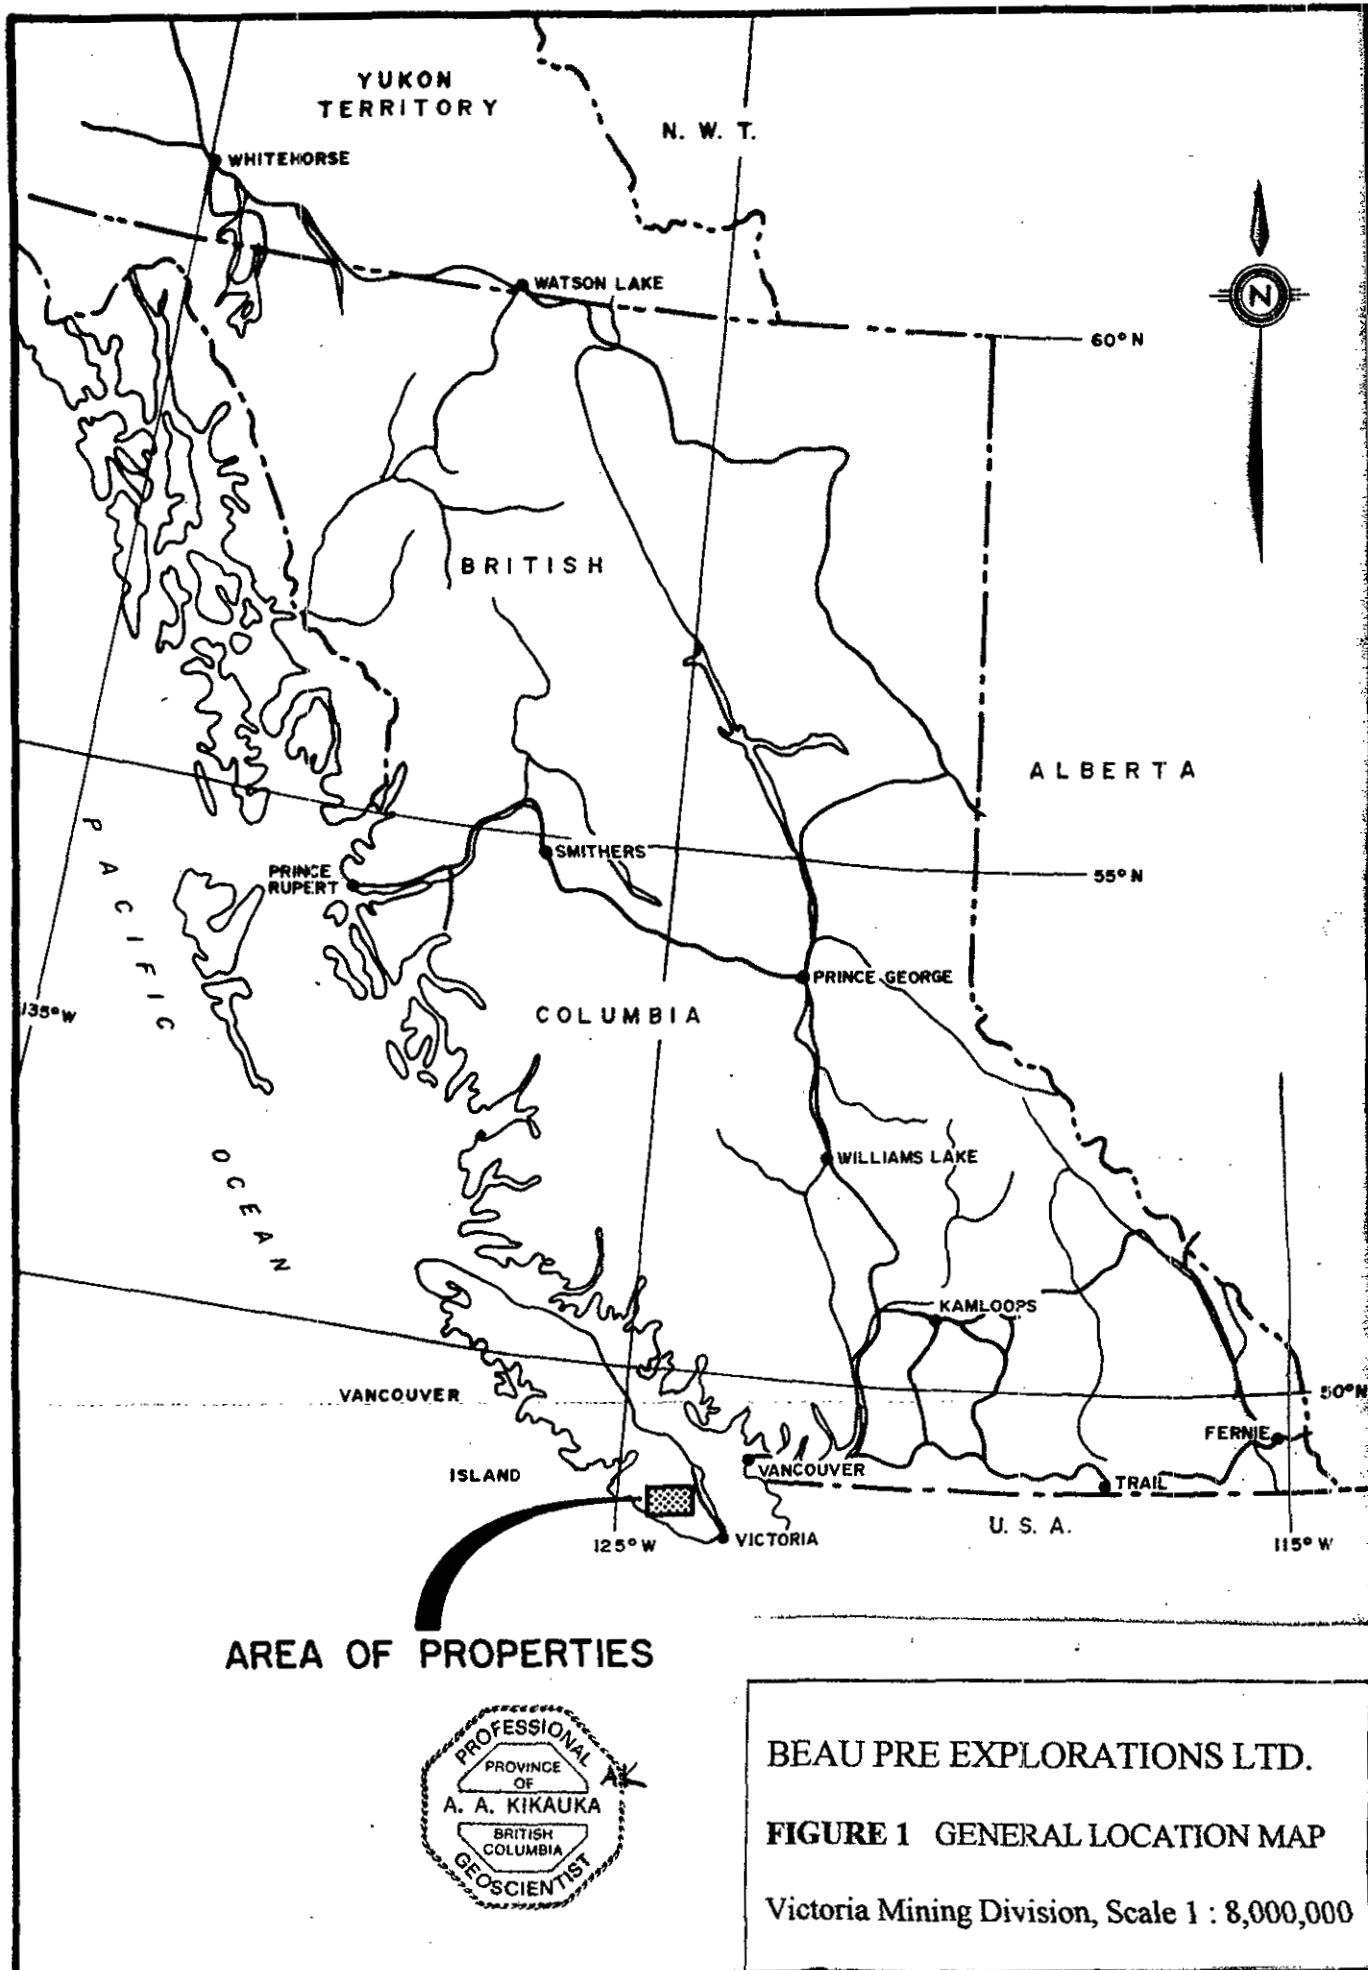

BRITISH COLUMBIA
MINISTRY OF ENERGY
AND MINES

ENERGY AND MINERALS DIVISION
MINERAL TITLES BRANCH

MINERAL TITLES REFERENCE

MAP 092C060

U.T.M. ZONE 10

LAST MAP UPDATE 1998 SEP 28 0 .5 1.0 Km



N

W

E

S

SW

SE

NE

NO

SO

SE

SW

SE


BEAU PRE EXPLORATIONS LTD.

FIGURE 3 TOPOGRAPHY & ACCESS ROADS: 'B' & 'C' VEIN TRENCH SITE

Victoria Mining Division, Scale 1 : 5,000

0 50 100 m.

N

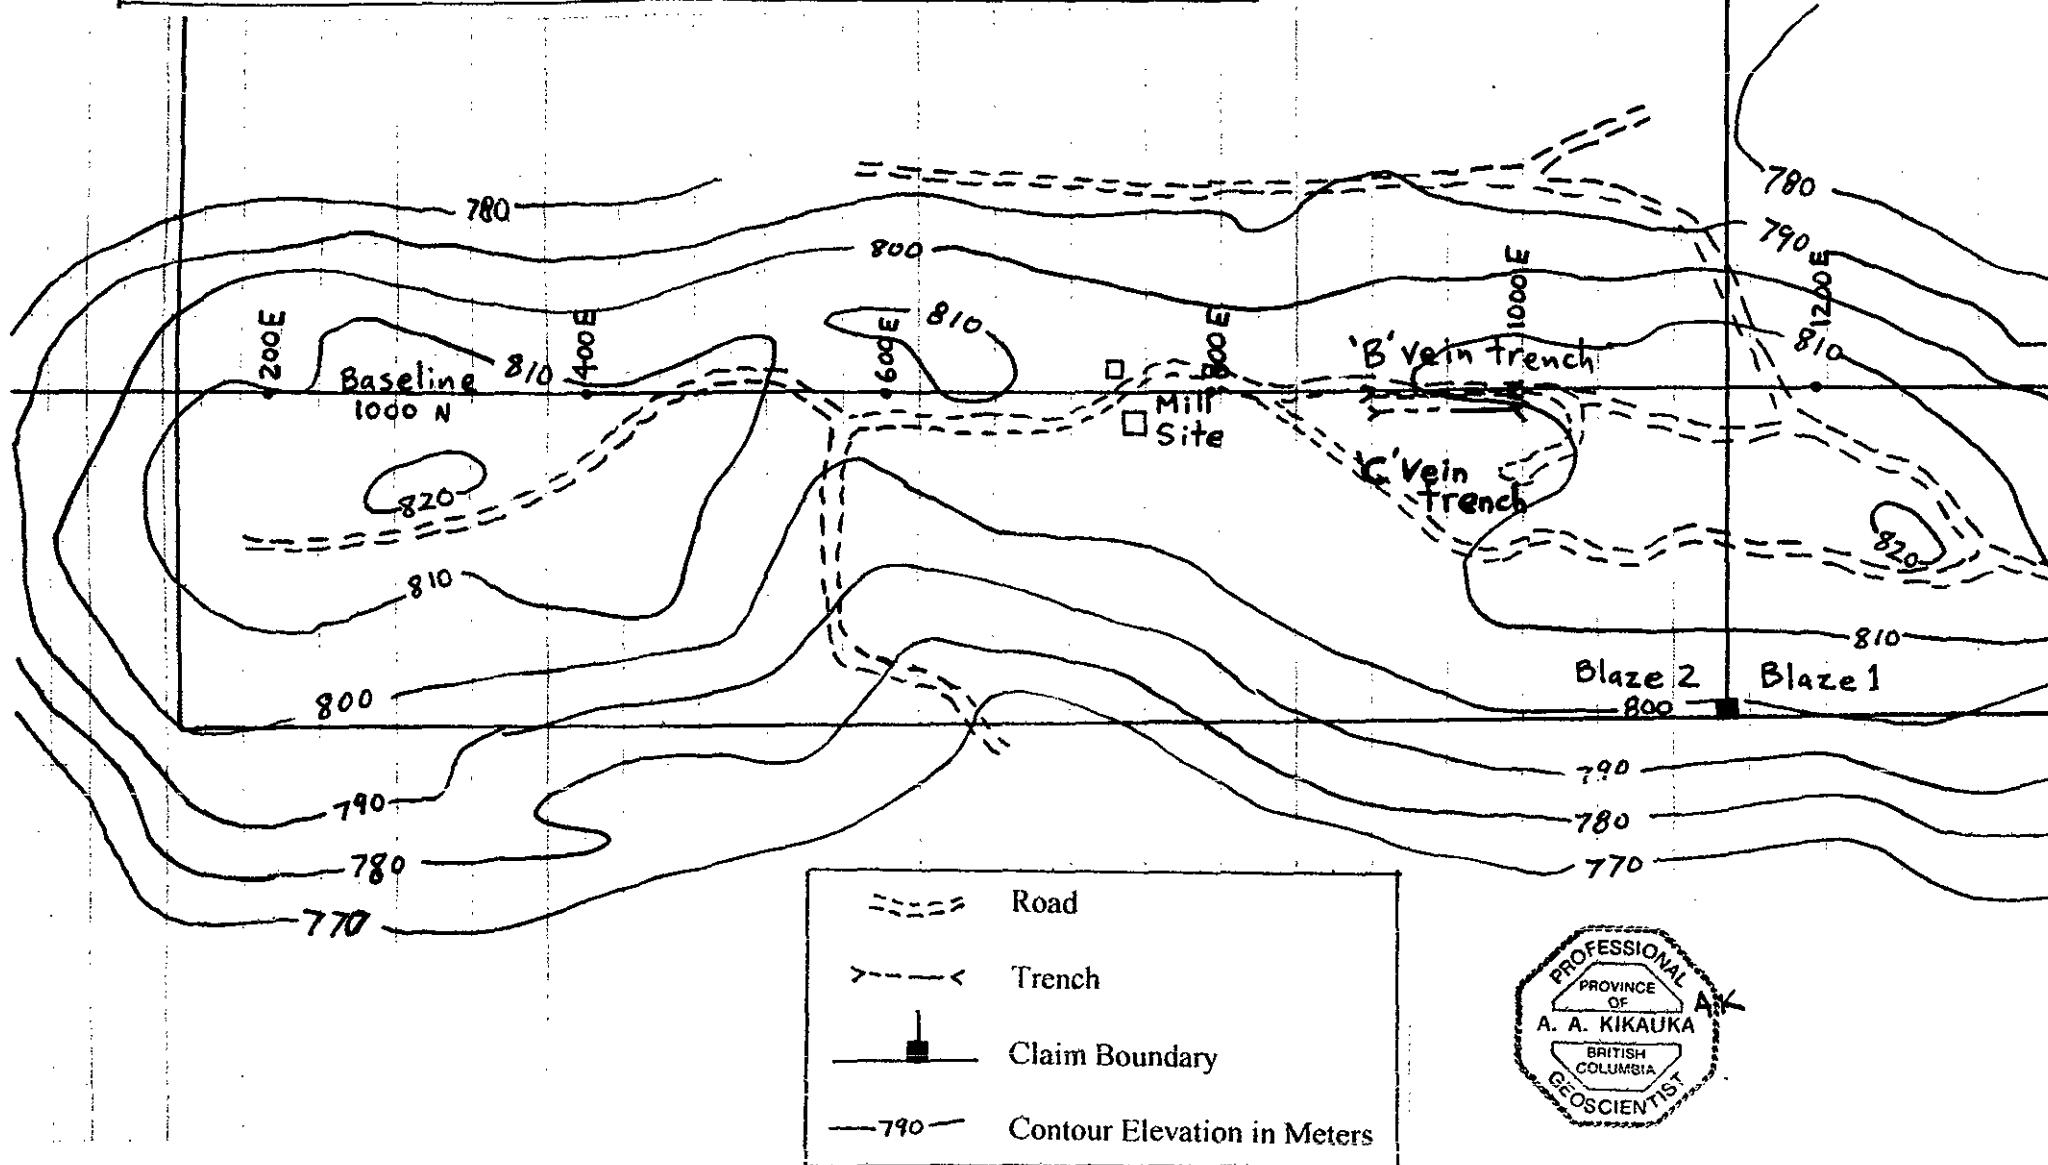

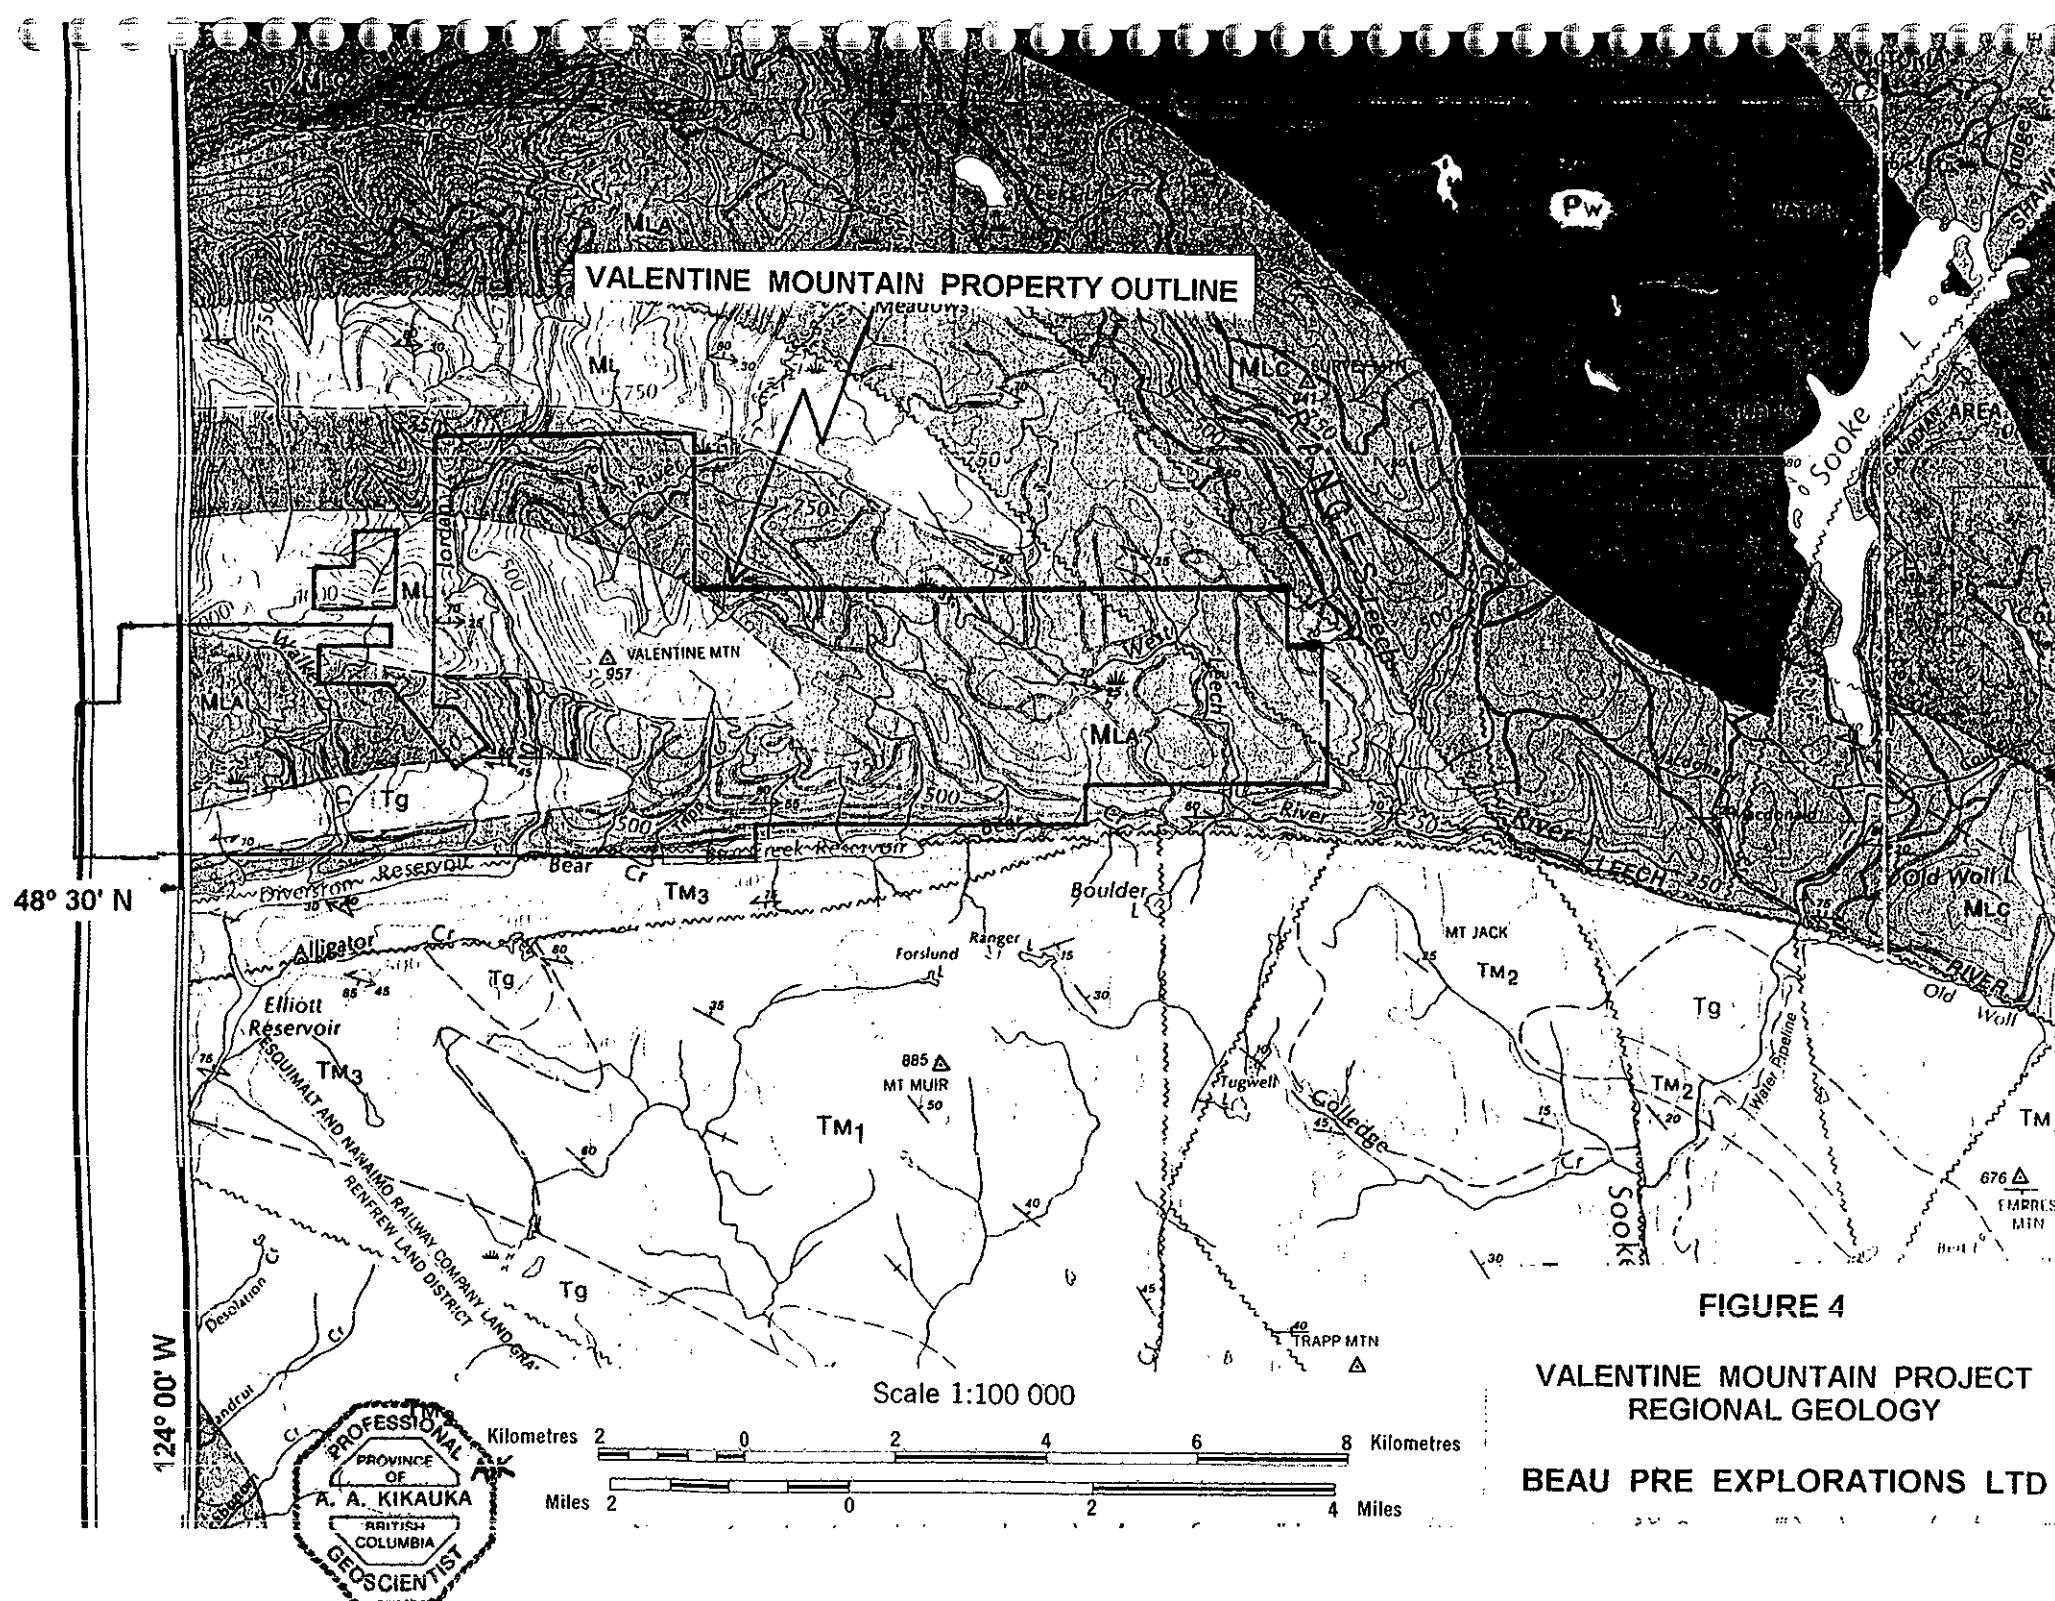


FIGURE 4


VALENTINE MOUNTAIN PROJECT REGIONAL GEOLOGY

BEAU PRE EXPLORATIONS LTD

LEGEND


TERTIARY

OLIGOCENE AND/OR MIocene



SOOKE FORMATION: conglomerate, sandstone, shale

EOCENE (AND OLDER?)



CATFACE INTRUSIONS: quartz diorite, agmatite



METCHOSIN VOLCANICS: TM₁: pillow basalt, breccia, tuff; TM₂: mainly basaltic lava; TM₃: schistose metavolcanic rock




SOOKE GABBRO: mainly gabbro

- Geological boundary, (approximate)*.....
 - Fault, (approximate)*.....
 - Anticlinal axis*
 - Synclinal axis*
 - Bedding, (inclined, vertical, overturned)*
 - Foliation (inclined, vertical, with plunge of lineation)*
 - Gneissosity, (inclined, vertical)*
-

Geology by J. E. Muller, 1970, 1980


JURASSIC AND CRETACEOUS

UPPER JURASSIC AND LOWER CRETACEOUS



SPIEDEN FORMATION: conglomerate, sandstone, siltstone

TRIASSIC TO CRETACEOUS




*LEECH RIVER FORMATION: (MLC to ML)
METAGREYWACKE UNIT: metagreywacke, meta-arkose,
quartz-feldspar-biotite schist*



*ARGILLITE-METAGREYWACKE UNIT: thinly bedded greywacke
and argillite, slate, phyllite, quartz-biotite schist*




*CHERT-ARGILLITE-VOLCANIC UNIT: ribbon chert,
cherty argillite, metarhyolite, metabasalt, chlorite schist*



*CONSTITUTION FORMATION (San Juan Island):
thinly bedded greywacke, argillite and chert*

JURASSIC


LOWER TO MIDDLE JURASSIC



ISLAND INTRUSIONS: granodiorite, quartz diorite



*BONANZA GROUP
Basaltic to rhyolitic tuff, breccia, flows, minor argillite, greywacke*




LOWER PALEOZOIC (OR YOUNGER?)

COLQUITZ GNEISS: quartz-feldspar gneiss




*WARK GNEISS: massive and gneissic metadiorite,
metagabbro, amphibolite*

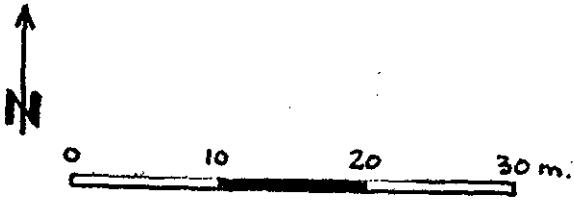


BEAU PRE EXPLORATIONS LTD.

FIGURE 5 DRILL PAD LOCATIONS FOR DDH 00-01 to 08: 'B' & 'C' VEIN TRENCH SITE

Victoria Mining Division, Scale 1 : 500

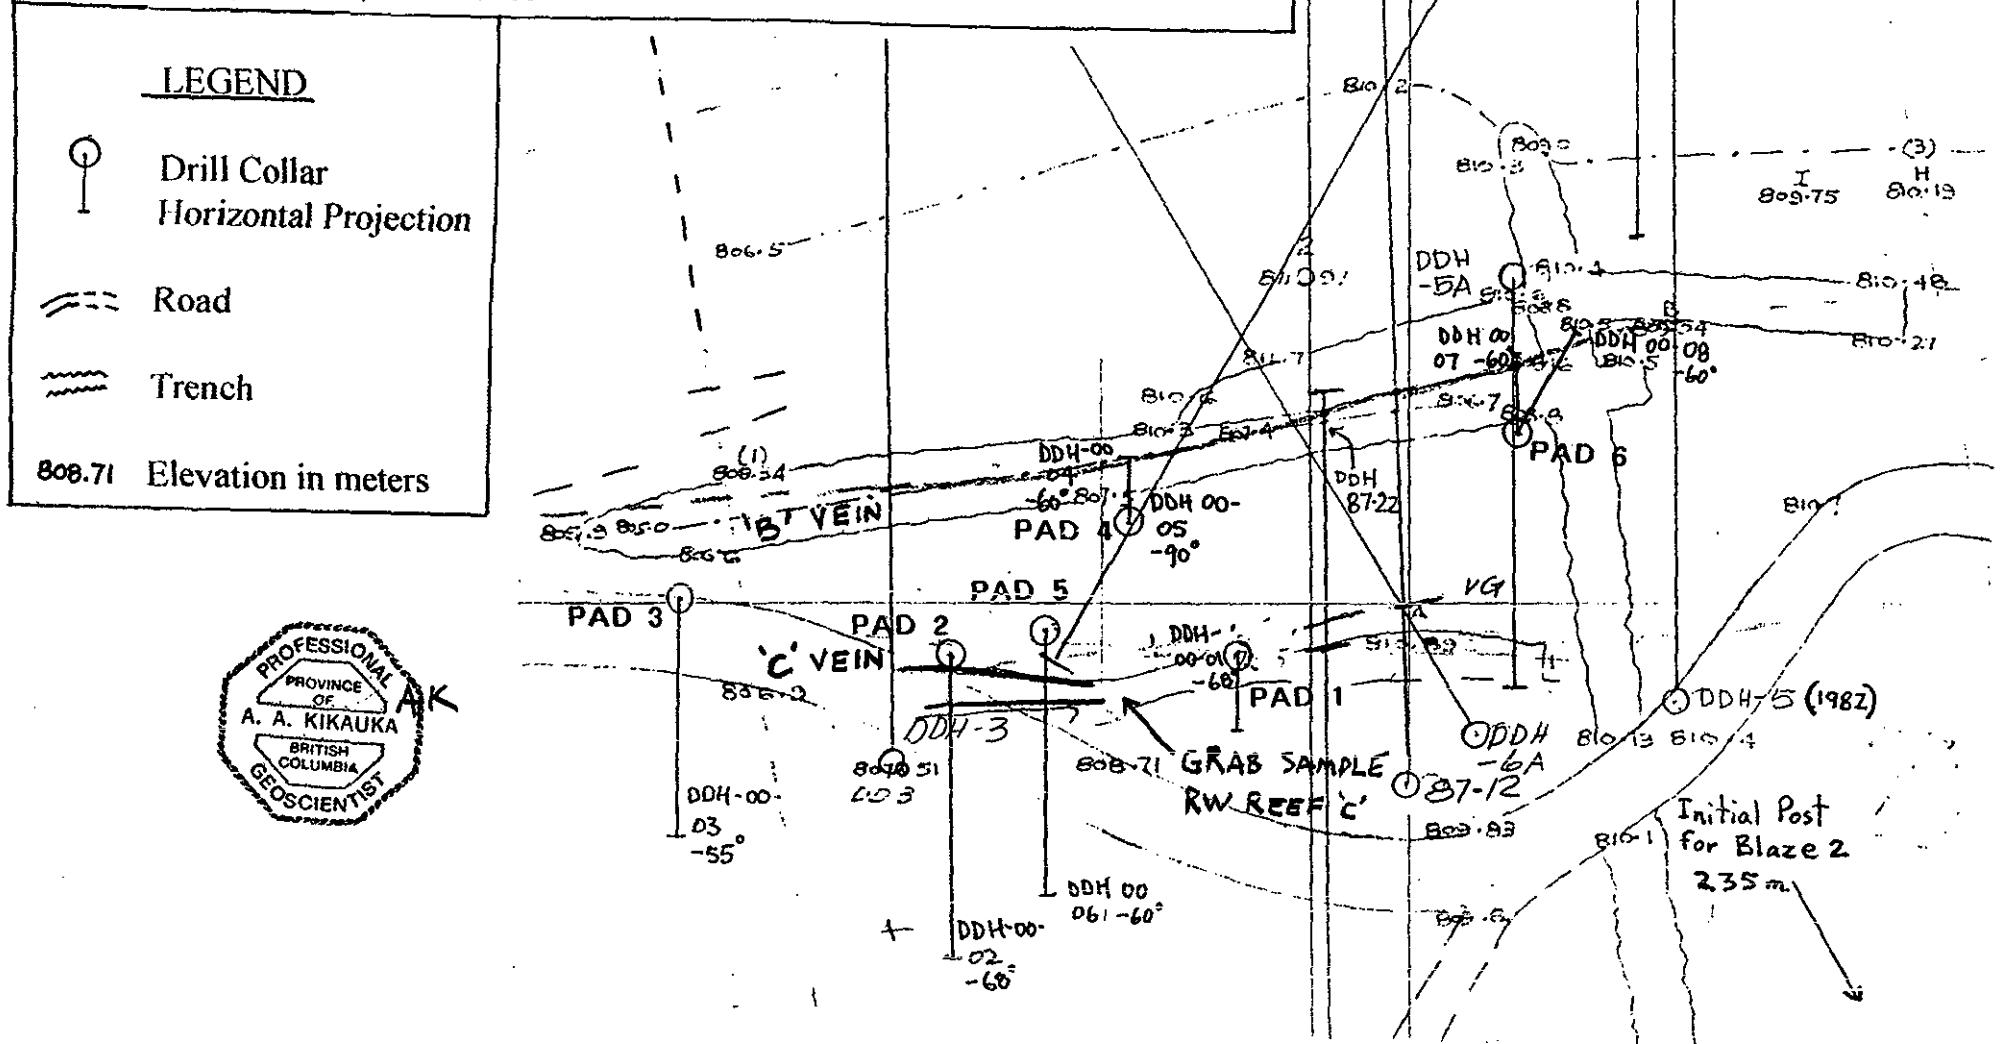

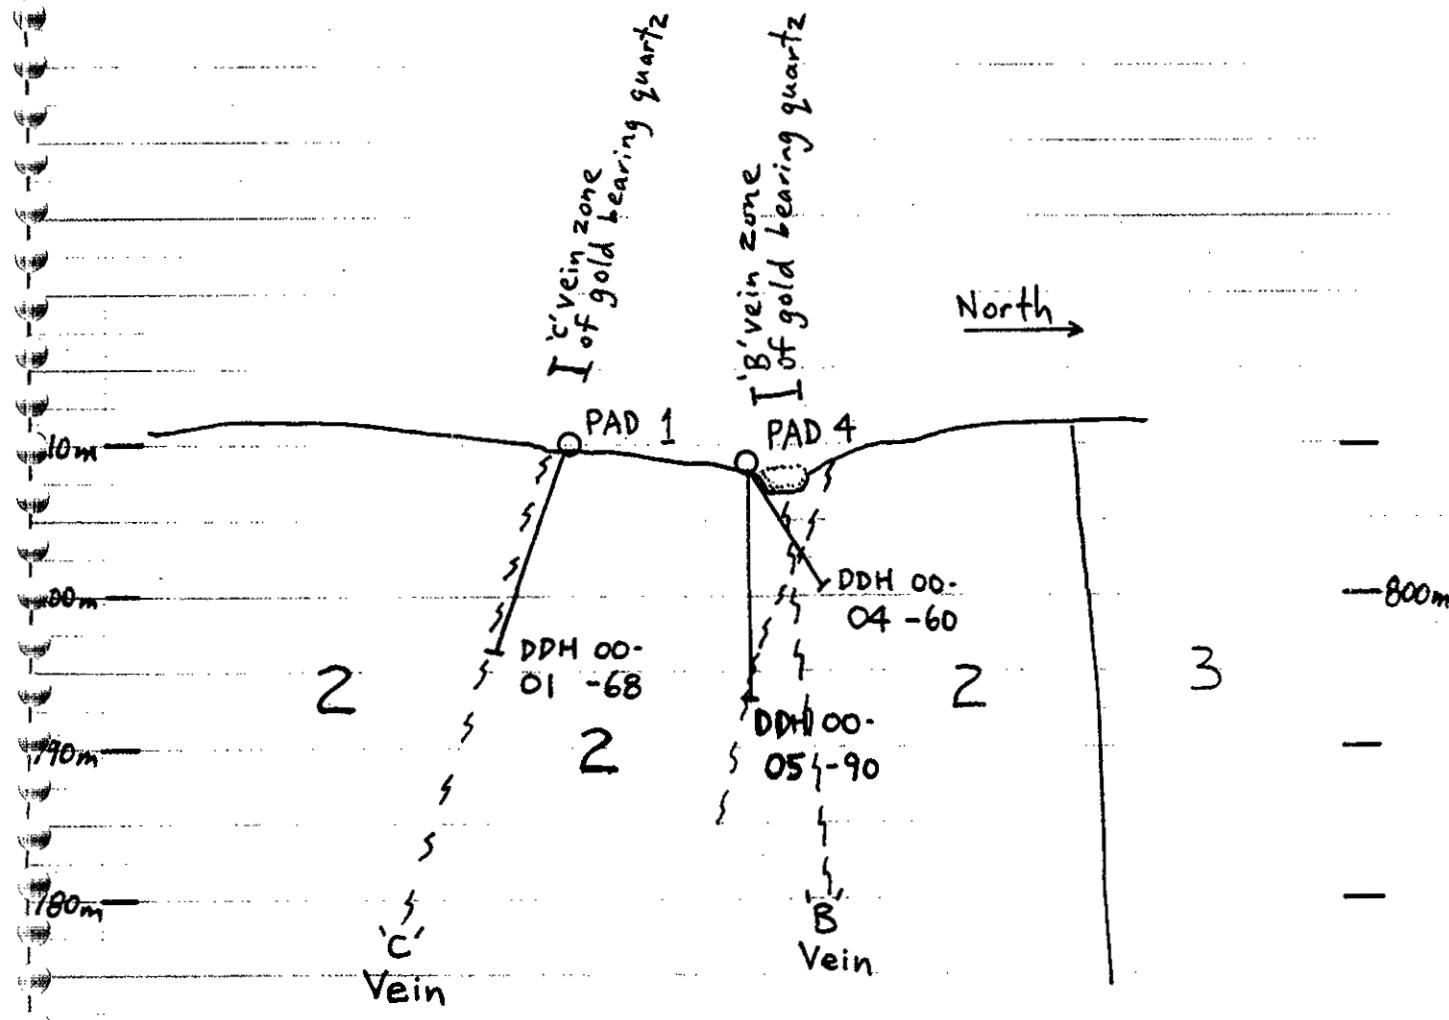

BEAU PRE EXPLORATIONS LTD.

FIG.6

CROSS SECTION 9+00 E: LOOKING NORTH
DIAMOND DRILL HOLE 00-01, 04, 05

TRIASSIC TO CRETACEOUS LEECH RIVER FM.

- 3 Amphibolite (Metamorphosed volcanics)
- 2 Biotite Gneiss (Metamorphosed sandstone)
- 1 Biotite Schist (Metamorphosed pelitic rocks)


— Fault and/or Fracture Zone

— Trace of trench



SCALE 1:500

0 10 20 m.

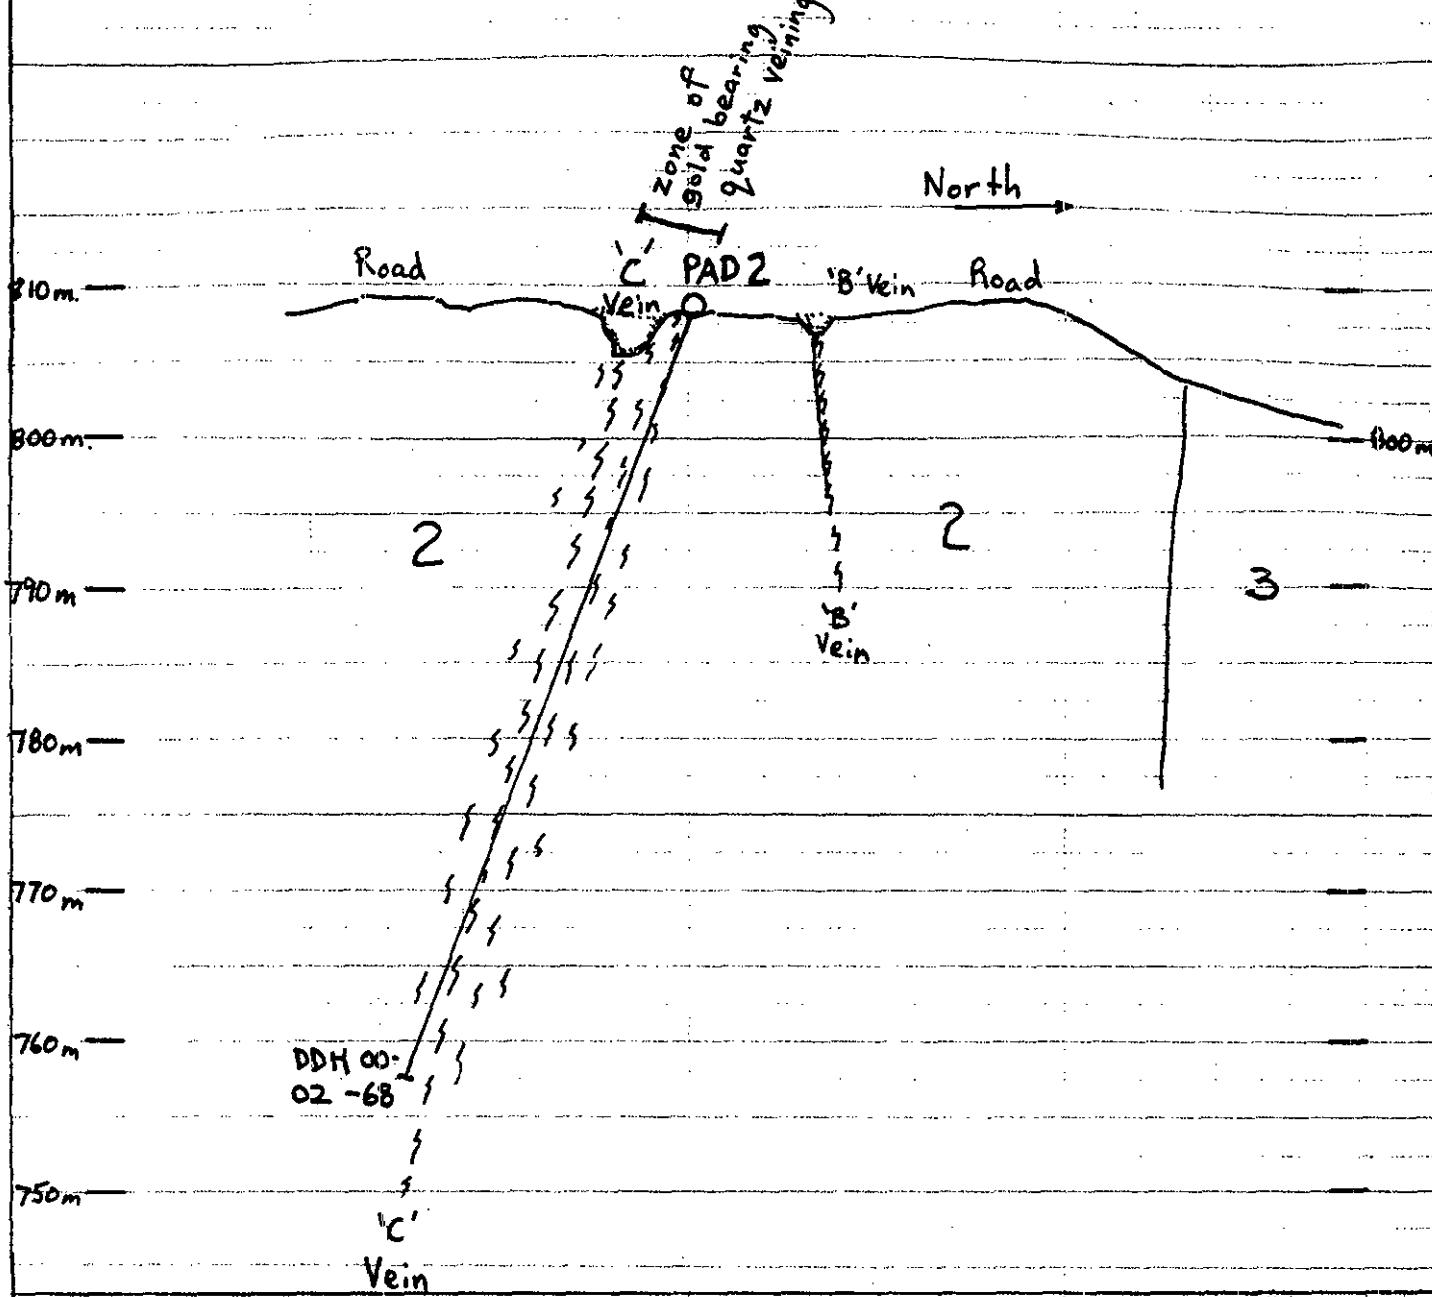

BEAU PRE EXPLORATIONS LTD.

FIG.7

CROSS SECTION 8+81.7 E: LOOKING NORTH
DIAMOND DRILL HOLE 00-02

TRIASSIC TO CRETACEOUS LEECH RIVER FM.



SCALE 1:500

- [3]
- [2]
- [1]


- Amphibolite (Metamorphosed volcanics)
- Biotite Gneiss (Metamorphosed sandstone)
- Biotite Schist (Metamorphosed pelitic rocks)

~~~~~ Fault and/or Fracture Zone



Trace of trench

0 10 20m.

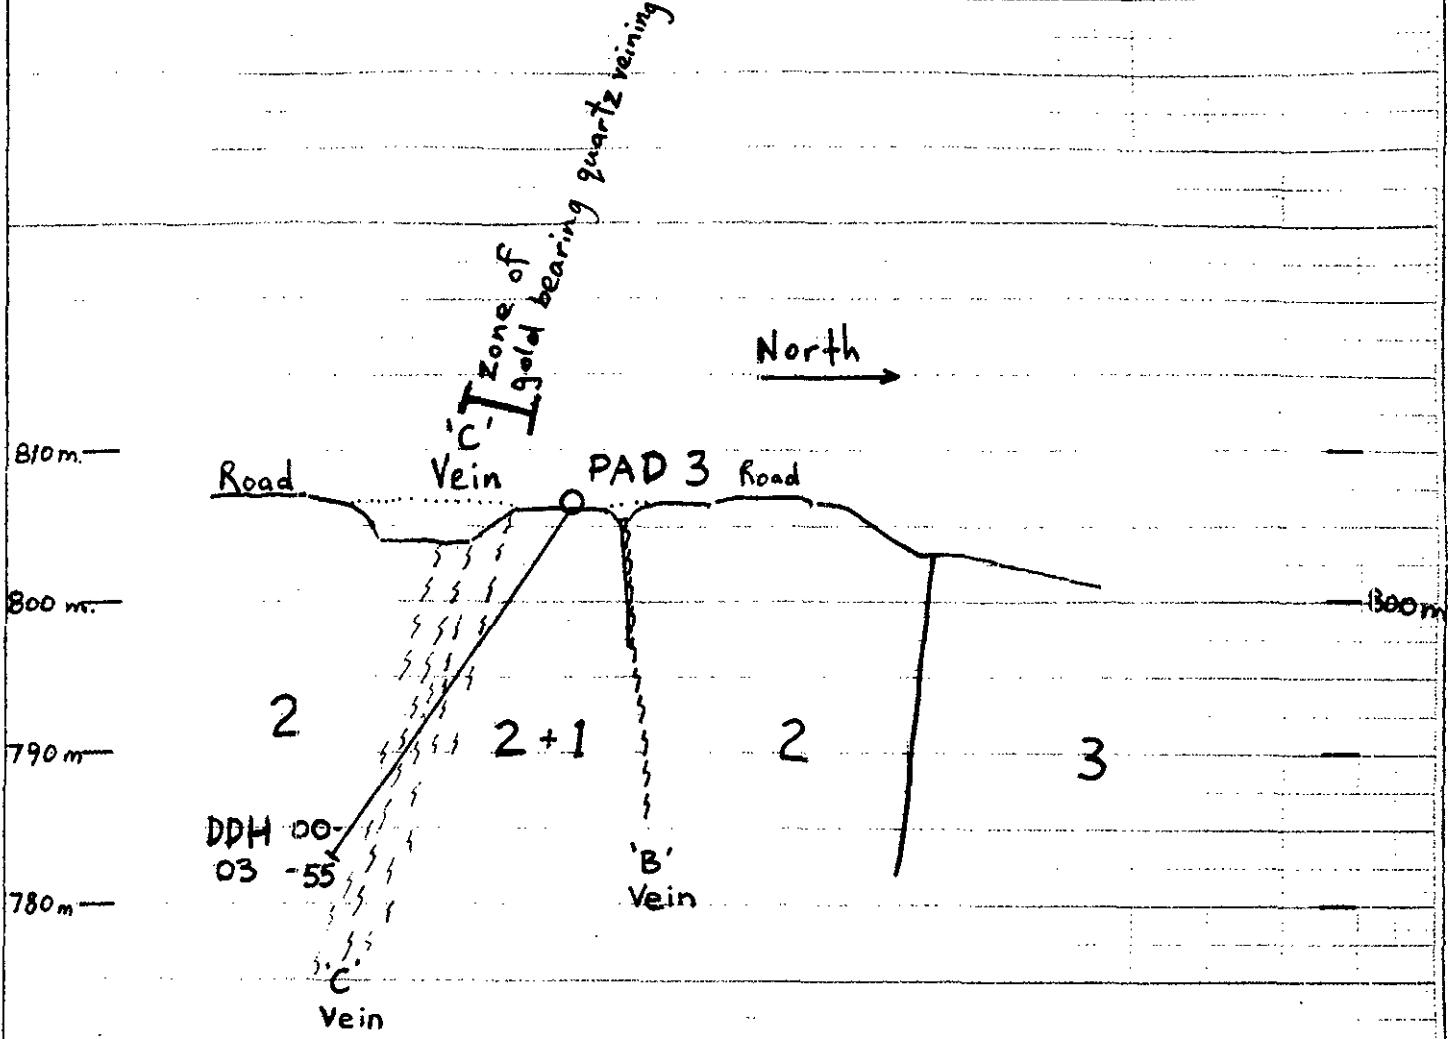

BEAU PRE EXPLORATIONS LTD.

FIG.8

CROSS SECTION 8+63.4 E: LOOKING NORTH  
DIAMOND DRILL HOLE 00-03

TRIASSIC TO CRETACEOUS LEECH RIVER FM.

- 3 Amphibolite (Metamorphosed volcanics)
- 2 Biotite Gneiss (Metamorphosed sandstone)
- 1 Biotite Schist (Metamorphosed pelitic rocks)


Fault and/or Fracture Zone

Trace of trench



SCALE 1:500

0 10 20m

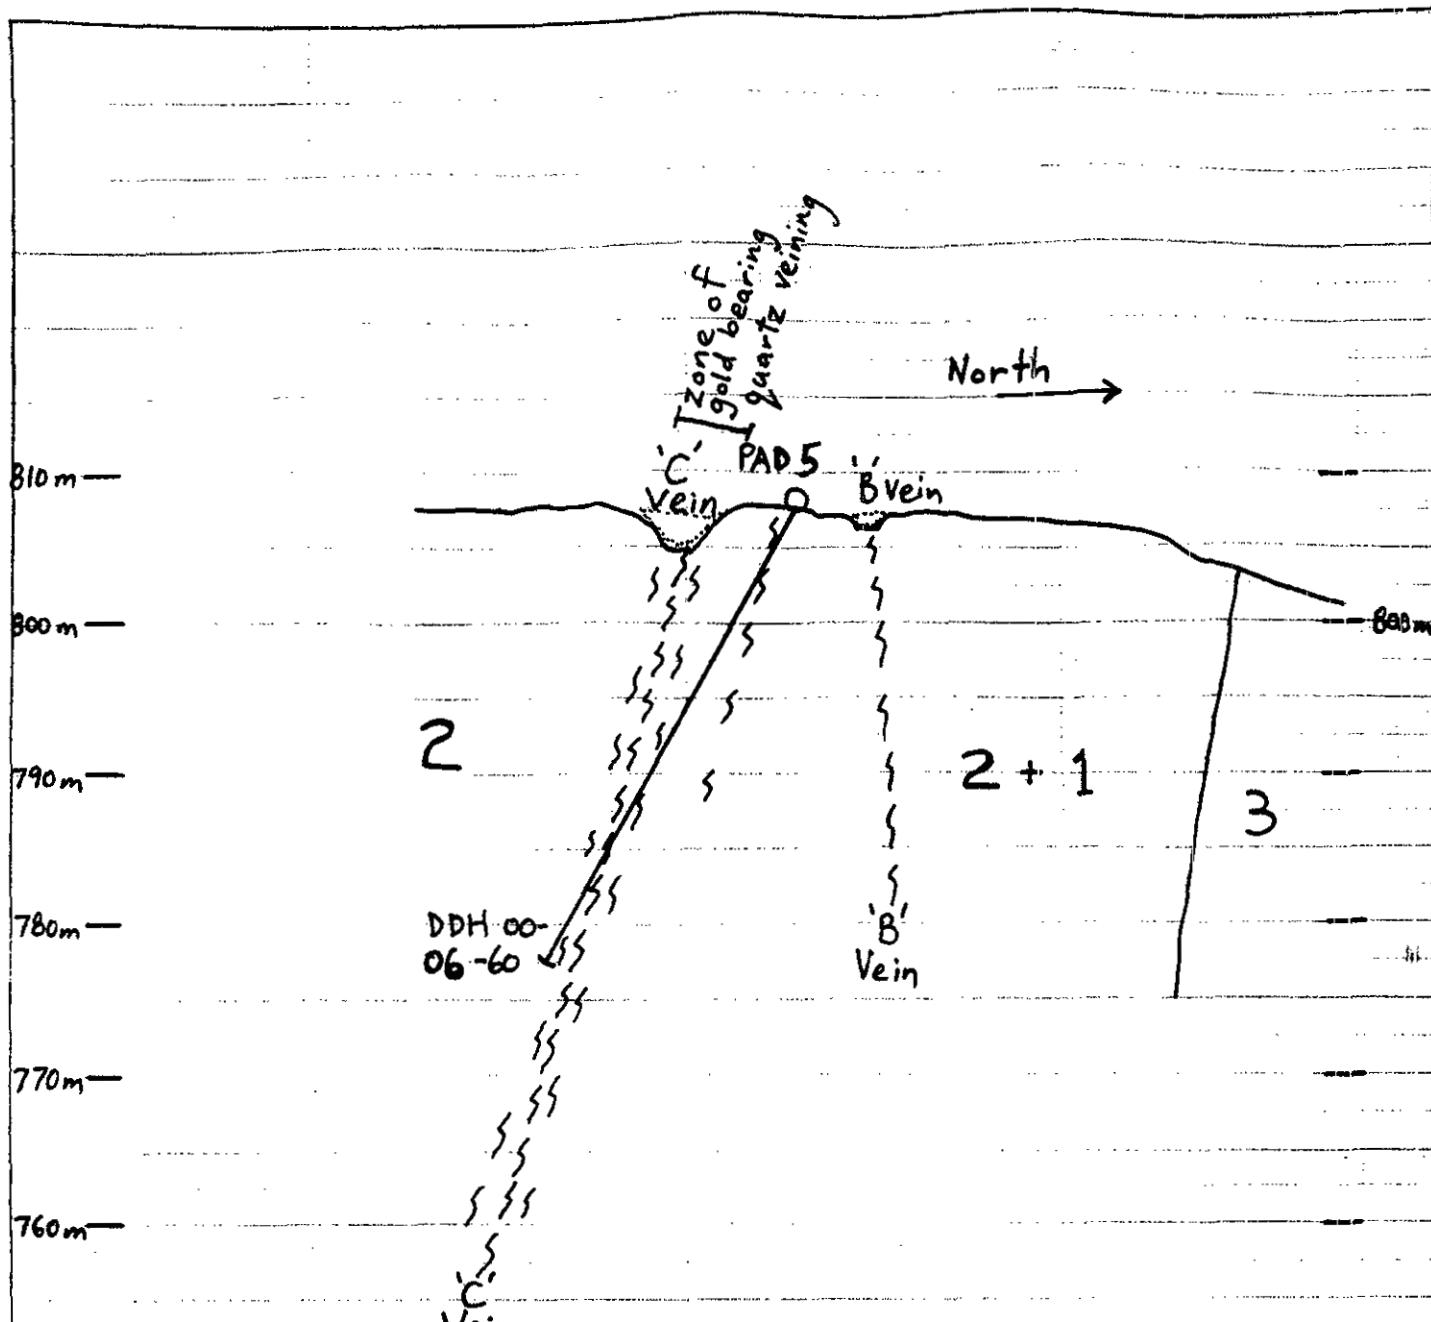

BEAU PRE EXPLORATIONS LTD.

FIG.9

CROSS SECTION 8+87.8 E: LOOKING NORTH  
DIAMOND DRILL HOLE 00-06

TRIASSIC TO CRETACEOUS LEECH RIVER FM.


- |   |                                              |
|---|----------------------------------------------|
| 3 | Amphibolite (Metamorphosed volcanics)        |
| 2 | Biotite Gneiss (Metamorphosed sandstone)     |
| 1 | Biotite Schist (Metamorphosed pelitic rocks) |

~~~ Fault and/or Fracture Zone

Trace of trench



SCALE 1:500

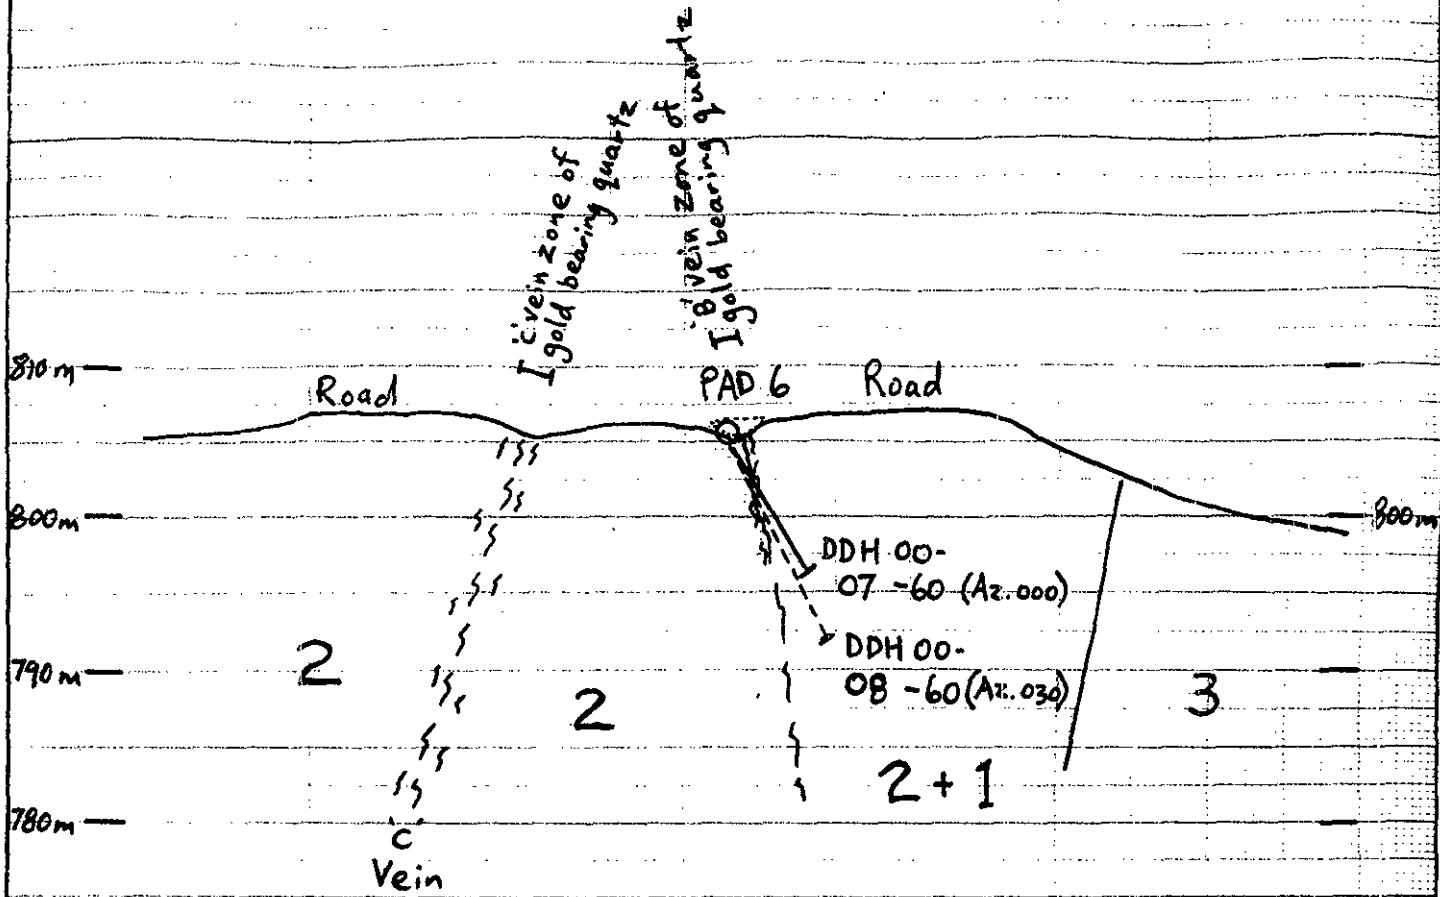

BEAU PRE EXPLORATIONS LTD.

FIG. 10

CROSS SECTION 9+18.7 E: LOOKING NORTH
DIAMOND DRILL HOLE 00-07, 08

TRIASSIC TO CRETACEOUS LEECH RIVER FM.

- 3** Amphibolite (Metamorphosed volcanics)
 - 2** Biotite Gneiss (Metamorphosed sandstone)
 - 1** Biotite Schist (Metamorphosed pelitic rocks)



SCALE 1:500

Fault and/or Fracture Zone

 Trace of trench



0 10 20m.

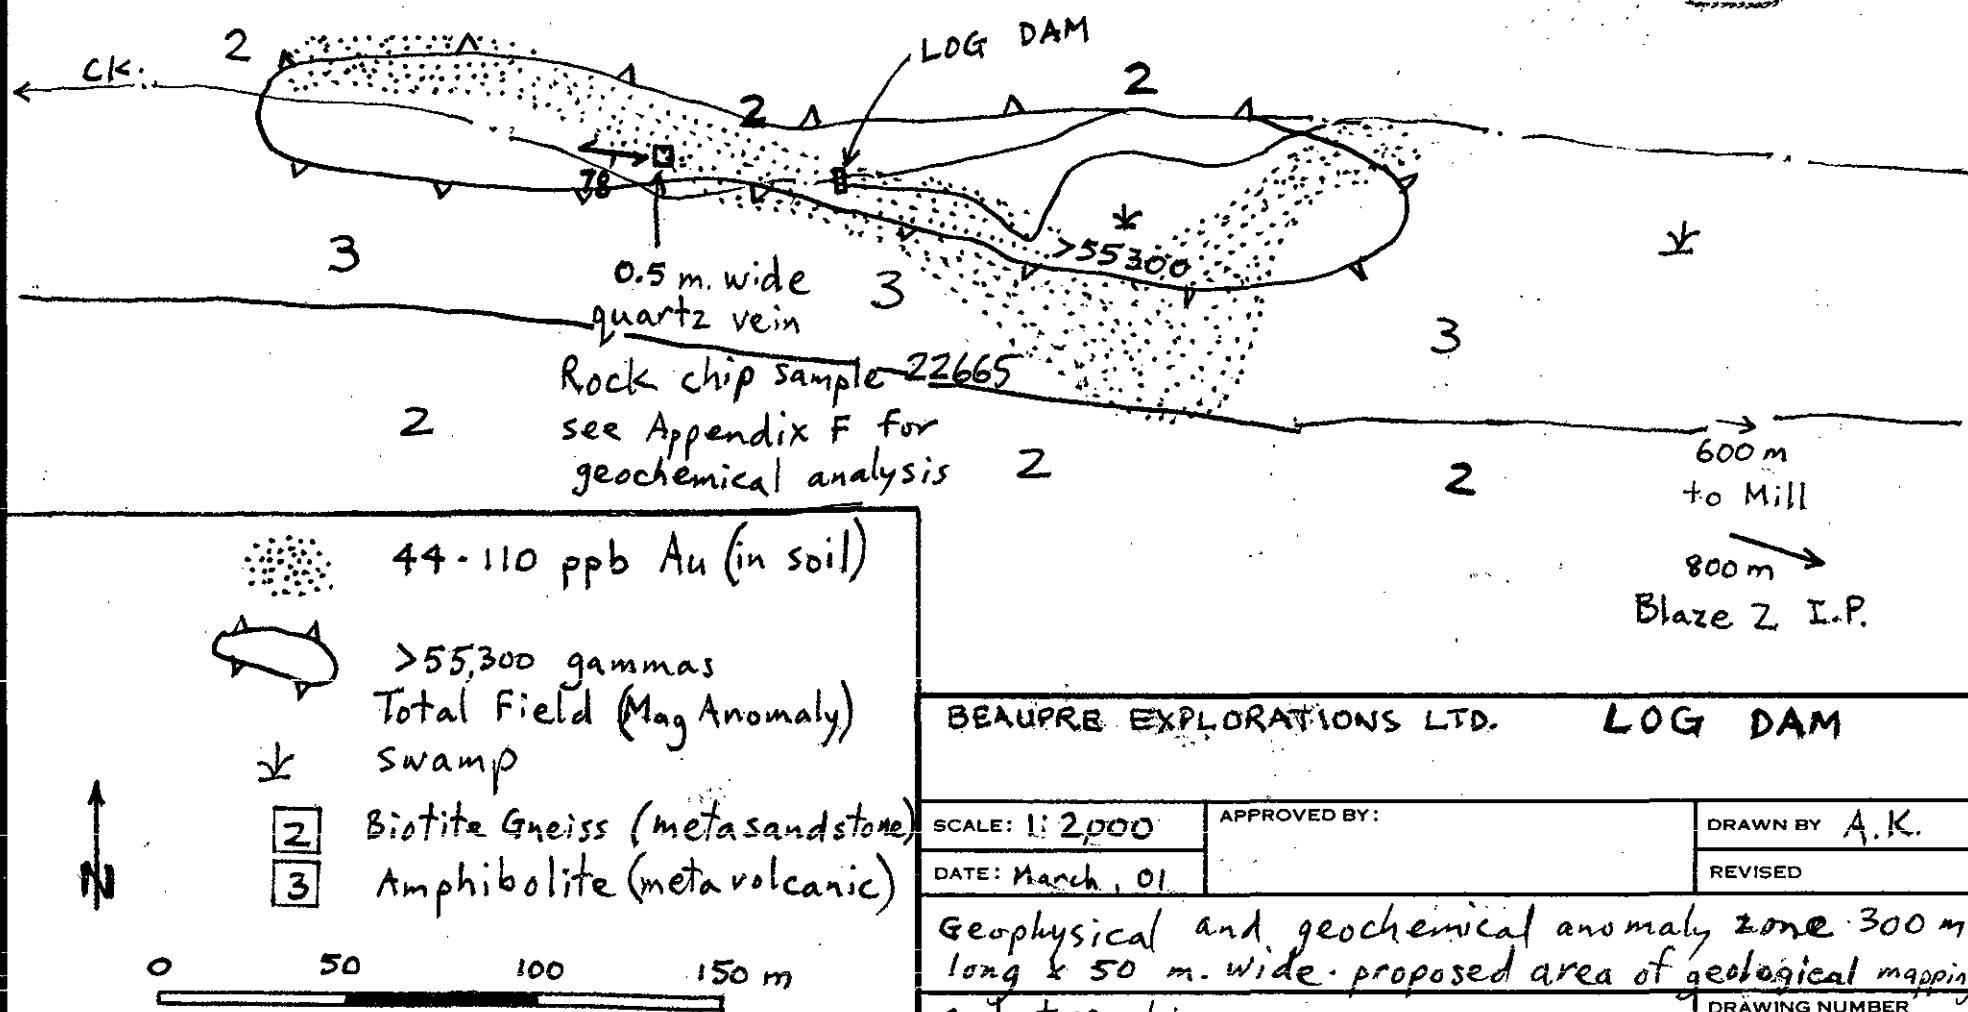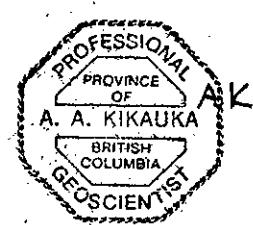

BEAUPRE EXPLORATIONS LTD.

LOG DAM

SCALE: 1:2000

DATE: March, 01

APPROVED BY

DRAWN BY A.K.

REVISED

Geochloris

Geophysical

geologer

Geophysical and geochemical anomaly zone 300 m long & 50 m. wide. proposed area of geological mapping and trenching.

DRAWING NUMBER

FIG. II

APPENDIX A

[•Ministry Home](#) [Government of British Columbia](#)
Programs & Services [Ministry of Energy & Mines](#)
[Ministry News](#) | [Ministry Search](#) | [Reports & Publications](#) | [Site Map](#) | [Contacts](#)

Mineral Titles Search by Owner

The mineral tenure information at this site was last updated on the morning of **January 30, 2001**.

Title Search by Owner

Name: Beau pre

Tenure Type: All

Standing: Good

Tenures held by BEAU PRE EXPLORATIONS LTD.:

There were 58 results.

| Tenure Number | Claim Name | Owner Number | Map Number | Work Recorded To | Status | Mining Division | Units | Tag Number |
|------------------------|------------|-----------------------------|------------|------------------|------------------------|-----------------|-------|------------|
| 260251 | BLAZE #1 | 101792 100% | 092B12W | 20020214 | Good Standing 20020214 | 24 Victoria | 1 | 357 |
| 260253 | BLAZE #2 | 101792 100% | 092B12W | 20010214 | Good Standing 20010214 | 24 Victoria | 2 | 729 |
| 260263 | BLAZE 3 | 101792 100% | 092B12W | 20010214 | Good Standing 20010214 | 24 Victoria | 12 | 41260 |
| 260306 | BLAZE #4 | 101792 100% | 092B12W | 20010214 | Good Standing 20010214 | 24 Victoria | 3 | 54919 |
| 260324 | BPEX #1 | 101792 100% | 092B12W | 20010214 | Good Standing 20010214 | 24 Victoria | 20 | 54921 |
| 260325 | BPEX #2 | 101792 100% | 092B12W | 20010214 | Good Standing 20010214 | 24 Victoria | 18 | 54923 |
| 260326 | BPEX #3 | 101792 100% | 092B12W | 20010214 | Good Standing 20010214 | 24 Victoria | 1 | 54924 |
| 260333 | BPEX #4 | 101792 100% | 092B12W | 20010214 | Good Standing 20010214 | 24 Victoria | 3 | 41261 |

| | | | | | | | | |
|---------------|---------------|--------------------|---------|----------|------------------------|-------------|----|---------|
| <u>260334</u> | BPEX #5 | <u>101792</u> 100% | 092B12W | 20010214 | Good Standing 20010214 | 24 Victoria | 1 | 54925 |
| <u>260335</u> | BPEX #6 | <u>101792</u> 100% | 092B12W | 20010214 | Good Standing 20010214 | 24 Victoria | 1 | 54926 |
| <u>260338</u> | BPEX #12 | <u>101792</u> 100% | 092B12W | 20010214 | Good Standing 20010214 | 24 Victoria | 14 | 55176 |
| <u>260354</u> | BPEX #7 | <u>101792</u> 100% | 092B12W | 20010214 | Good Standing 20010214 | 24 Victoria | 8 | 72272 |
| <u>260381</u> | BPEX 9 | <u>101792</u> 100% | 092B12W | 20010214 | Good Standing 20010214 | 24 Victoria | 16 | 72273 |
| <u>260414</u> | JORDAN GOLD 5 | <u>101792</u> 100% | 092B12W | 20010214 | Good Standing 20010214 | 24 Victoria | 18 | 86354 |
| <u>260415</u> | LUSTER #2 | <u>101792</u> 100% | 092B12W | 20020214 | Good Standing 20020214 | 24 Victoria | 18 | 55179 |
| <u>260418</u> | LUSTER #1 | <u>101792</u> 100% | 092B12W | 20010214 | Good Standing 20010214 | 24 Victoria | 2 | 85009 |
| <u>261022</u> | DORAN 1 | <u>101792</u> 100% | 092B12W | 20010214 | Good Standing 20010214 | 24 Victoria | 2 | 28258 |
| <u>261023</u> | DORAN 2 FR | <u>101792</u> 100% | 092B12W | 20010214 | Good Standing 20010214 | 24 Victoria | 1 | 28259 |
| <u>261042</u> | DORAN 5 FR | <u>101792</u> 100% | 092B12W | 20020214 | Good Standing 20020214 | 24 Victoria | 1 | 28306 |
| <u>320947</u> | EDEN | <u>101792</u> 100% | 092C060 | 20010214 | Good Standing 20010214 | 24 Victoria | 1 | 654078M |
| <u>355196</u> | GS 1 | <u>101792</u> 100% | 092B12W | 20010214 | Good Standing 20010214 | 24 Victoria | 1 | 640155M |
| <u>355197</u> | GS 2 | <u>101792</u> 100% | 092B12W | 20010214 | Good Standing 20010214 | 24 Victoria | 1 | 640156M |
| <u>355198</u> | GS 3 | <u>101792</u> 100% | 092B12W | 20010214 | Good Standing 20010214 | 24 Victoria | 1 | 640157M |
| <u>355610</u> | A1 | <u>101792</u> 100% | 092B12W | 20010214 | Good Standing 20010214 | 24 Victoria | 1 | 672426M |

| | | | | | | | | |
|---------------|----------|--------------------|---------|----------|------------------------|-------------|----|---------|
| <u>355611</u> | A2 | <u>101792</u> 100% | 092B12W | 20010214 | Good Standing 20010214 | 24 Victoria | 1 | 672427M |
| <u>355612</u> | A3 | <u>101792</u> 100% | 092B12W | 20010214 | Good Standing 20010214 | 24 Victoria | 1 | 672428M |
| <u>355613</u> | A4 | <u>101792</u> 100% | 092B12W | 20010214 | Good Standing 20010214 | 24 Victoria | 1 | 672429M |
| <u>355614</u> | A5 | <u>101792</u> 100% | 092B12W | 20010214 | Good Standing 20010214 | 24 Victoria | 1 | 640147M |
| <u>355615</u> | A6 | <u>101792</u> 100% | 092B12W | 20010214 | Good Standing 20010214 | 24 Victoria | 1 | 640148M |
| <u>355616</u> | A7 | <u>101792</u> 100% | 092B12W | 20010214 | Good Standing 20010214 | 24 Victoria | 1 | 640169M |
| <u>355617</u> | A8 | <u>101792</u> 100% | 092B12W | 20010214 | Good Standing 20010214 | 24 Victoria | 1 | 640170M |
| <u>355618</u> | A9 | <u>101792</u> 100% | 092B12W | 20010214 | Good Standing 20010214 | 24 Victoria | 1 | 640171M |
| <u>355619</u> | A10 | <u>101792</u> 100% | 092B12W | 20010214 | Good Standing 20010214 | 24 Victoria | 1 | 640172M |
| <u>355620</u> | A11 | <u>101792</u> 100% | 092B12W | 20010214 | Good Standing 20010214 | 24 Victoria | 1 | 640173M |
| <u>355621</u> | A12 | <u>101792</u> 100% | 092B12W | 20010214 | Good Standing 20010214 | 24 Victoria | 1 | 640174M |
| <u>355622</u> | A13 | <u>101792</u> 100% | 092B12W | 20010214 | Good Standing 20010214 | 24 Victoria | 1 | 640175M |
| <u>362862</u> | WALKER 1 | <u>101792</u> 100% | 092B12W | 20010214 | Good Standing 20010214 | 24 Victoria | 20 | 98177 |
| <u>362863</u> | LUSTER 3 | <u>101792</u> 100% | 092B12W | 20010214 | Good Standing 20010214 | 24 Victoria | 20 | 98321 |
| <u>362864</u> | B24 | <u>101792</u> 100% | 092B12W | 20010214 | Good Standing 20010214 | 24 Victoria | 1 | 685035M |
| <u>362865</u> | B23 | <u>101792</u> 100% | 092B12W | 20010214 | Good Standing 20010214 | 24 Victoria | 1 | 685034M |

| | | | | | | | | |
|---------------|-----|--------------------|---------|----------|------------------------|-------------|---|---------|
| <u>362866</u> | B22 | <u>101792</u> 100% | 092B12W | 20010214 | Good Standing 20010214 | 24 Victoria | 1 | 685033M |
| <u>362867</u> | B21 | <u>101792</u> 100% | 092B12W | 20010214 | Good Standing 20010214 | 24 Victoria | 1 | 685032M |
| <u>362868</u> | B20 | <u>101792</u> 100% | 092B12W | 20010214 | Good Standing 20010214 | 24 Victoria | 1 | 685031M |
| <u>362869</u> | B19 | <u>101792</u> 100% | 092B12W | 20010214 | Good Standing 20010214 | 24 Victoria | 1 | 685030M |
| <u>362870</u> | B18 | <u>101792</u> 100% | 092B12W | 20010214 | Good Standing 20010214 | 24 Victoria | 1 | 685029M |
| <u>362871</u> | B17 | <u>101792</u> 100% | 092B12W | 20010214 | Good Standing 20010214 | 24 Victoria | 1 | 685028M |
| <u>362872</u> | B16 | <u>101792</u> 100% | 092B12W | 20010214 | Good Standing 20010214 | 24 Victoria | 1 | 685027M |
| <u>362873</u> | B15 | <u>101792</u> 100% | 092B12W | 20010214 | Good Standing 20010214 | 24 Victoria | 1 | 685026M |
| <u>362874</u> | B14 | <u>101792</u> 100% | 092B12W | 20010214 | Good Standing 20010214 | 24 Victoria | 1 | 685025M |
| <u>362875</u> | B13 | <u>101792</u> 100% | 092B12W | 20010214 | Good Standing 20010214 | 24 Victoria | 1 | 685024M |
| <u>362876</u> | B6 | <u>101792</u> 100% | 092B12W | 20010214 | Good Standing 20010214 | 24 Victoria | 1 | 685013M |
| <u>362877</u> | B5 | <u>101792</u> 100% | 092B12W | 20010214 | Good Standing 20010214 | 24 Victoria | 1 | 685012M |
| <u>362878</u> | B4 | <u>101792</u> 100% | 092B12W | 20010214 | Good Standing 20010214 | 24 Victoria | 1 | 685011M |
| <u>362879</u> | B3 | <u>101792</u> 100% | 092B12W | 20010214 | Good Standing 20010214 | 24 Victoria | 1 | 685010M |
| <u>362880</u> | B2 | <u>101792</u> 100% | 092B12W | 20010214 | Good Standing 20010214 | 24 Victoria | 1 | 685009M |
| <u>362881</u> | B1 | <u>101792</u> 100% | 092B12W | 20010214 | Good Standing 20010214 | 24 Victoria | 1 | 685008M |

| | | | | | | | | |
|--------|----------|-------------|---------|----------|------------------------|-------------|----|-------|
| 365460 | WALKER 2 | 101792 100% | 092B12W | 20010214 | Good Standing 20010214 | 24 Victoria | 18 | 98340 |
| 365461 | WALKER 3 | 101792 100% | 092B12W | 20010214 | Good Standing 20010214 | 24 Victoria | 6 | 98341 |

Your use of this site is subject to this [disclaimer](#).

To download this information to a comma delimited text file [click here](#).

Shortcuts: [[Main Menu](#)] [[Free Miner](#)] [[Tenure Number](#)] [[Owner](#)] [[Locator](#)] [[Map](#)] [[Claim Name](#)] [[Tag Number](#)] [[Lot](#)]

Last date page updated November 12, 1999.

[[Top](#) • [Copyright](#) • [Disclaimer](#) • [Privacy](#)]

[[Feedback](#)]

[•Ministry Home](#) •Government of British Columbia
Programs & Services Ministry of Energy & Mines
[Ministry News](#) | [Ministry Search](#) | [Reports & Publications](#) | [Site Map](#) | [Contacts](#)

Mineral Titles Search by Owner

The mineral tenure information at this site was last updated on the morning of **January 30, 2001**.

Title Search by Owner

Name: Beaupre, Robert

Tenure Type: All

Standing: Good

Tenures held by BEAUPRE, ROBERT CHARLES:

There were 24 results.

| Tenure Number | Claim Name | Owner Number | Map Number | Work Recorded To | Status | Mining Division | Units | Tag Number |
|---------------|------------|--------------|------------|------------------|------------------------|-----------------|-------|------------|
| 269465 | | 101848 100% | 092B12W | 20011231 | Good Standing 20011231 | 24 Victoria | 0 | P32753 |
| 269466 | | 101848 100% | 092B12W | 20011231 | Good Standing 20011231 | 24 Victoria | 0 | P32754 |
| 269467 | | 101848 100% | 092B12W | 20011231 | Good Standing 20011231 | 24 Victoria | 0 | P32755 |
| 336403 | RB-1 | 101848 100% | 092B12W | 20010214 | Good Standing 20010214 | 24 Victoria | 1 | 663917M |
| 336404 | RB-2 | 101848 100% | 092B12W | 20010214 | Good Standing 20010214 | 24 Victoria | 1 | 663913M |
| 336405 | RB-5 | 101848 100% | 092B12W | 20010214 | Good Standing 20010214 | 24 Victoria | 1 | 663916M |
| 336406 | RB-6 | 101848 100% | 092B12W | 20010214 | Good Standing 20010214 | 24 Victoria | 1 | 663918M |
| 336407 | RB-3 | 101848 100% | 092B12W | 20010214 | Good Standing 20010214 | 24 Victoria | 1 | 663914M |
| 336408 | RB-4 | 101848 100% | 092B12W | 20010214 | Good Standing 20010214 | 24 Victoria | 1 | 663915M |
| 336409 | RB-7 | 101848 100% | 092B12W | 20010214 | Good Standing 20010214 | 24 Victoria | 1 | 663919M |
| 336410 | RB-8 | 101848 100% | 092B12W | 20010214 | Good Standing 20010214 | 24 Victoria | 1 | 663920M |


| | | | | | | | | |
|---------------|-------|-------------|---------|----------|---------------------------|-------------|---|---------|
| <u>336411</u> | RB-9 | 101848 100% | 092B12W | 20010214 | Good Standing
20010214 | 24 Victoria | 1 | 663921M |
| <u>336412</u> | RB-10 | 101848 100% | 092B12W | 20010214 | Good Standing
20010214 | 24 Victoria | 1 | 663922M |
| <u>336413</u> | RB-11 | 101848 100% | 092B12W | 20010214 | Good Standing
20010214 | 24 Victoria | 1 | 663923M |
| <u>336414</u> | RB-12 | 101848 100% | 092B12W | 20010214 | Good Standing
20010214 | 24 Victoria | 1 | 663924M |
| <u>336415</u> | RB-13 | 101848 100% | 092B12W | 20010214 | Good Standing
20010214 | 24 Victoria | 1 | 663925M |
| <u>336416</u> | RB-14 | 101848 100% | 092B12W | 20010214 | Good Standing
20010214 | 24 Victoria | 1 | 663926M |
| <u>336417</u> | RB-15 | 101848 100% | 092B12W | 20010214 | Good Standing
20010214 | 24 Victoria | 1 | 663927M |
| <u>336418</u> | RB-16 | 101848 100% | 092B12W | 20010214 | Good Standing
20010214 | 24 Victoria | 1 | 663928M |
| <u>336419</u> | RB-17 | 101848 100% | 092B12W | 20010214 | Good Standing
20010214 | 24 Victoria | 1 | 663929M |
| <u>336420</u> | RB-18 | 101848 100% | 092B12W | 20010214 | Good Standing
20010214 | 24 Victoria | 1 | 663930M |
| <u>336421</u> | RB-19 | 101848 100% | 092B12W | 20010214 | Good Standing
20010214 | 24 Victoria | 1 | 663931M |
| <u>336422</u> | RB-20 | 101848 100% | 092B12W | 20010214 | Good Standing
20010214 | 24 Victoria | 1 | 663932M |
| <u>336423</u> | RB-21 | 101848 100% | 092B12W | 20010214 | Good Standing
20010214 | 24 Victoria | 1 | 663933M |

Your use of this site is subject to this [disclaimer](#).

To download this information to a comma delimited text file [click here](#).


Shortcuts: [[Main Menu](#)] [[Free Miner](#)] [[Tenure Number](#)] [[Owner](#)] [[Locator](#)] [[Map](#)] [[Claim Name](#)] [[Tag Number](#)] [[Lot](#)]

Last date page updated November 12, 1999.

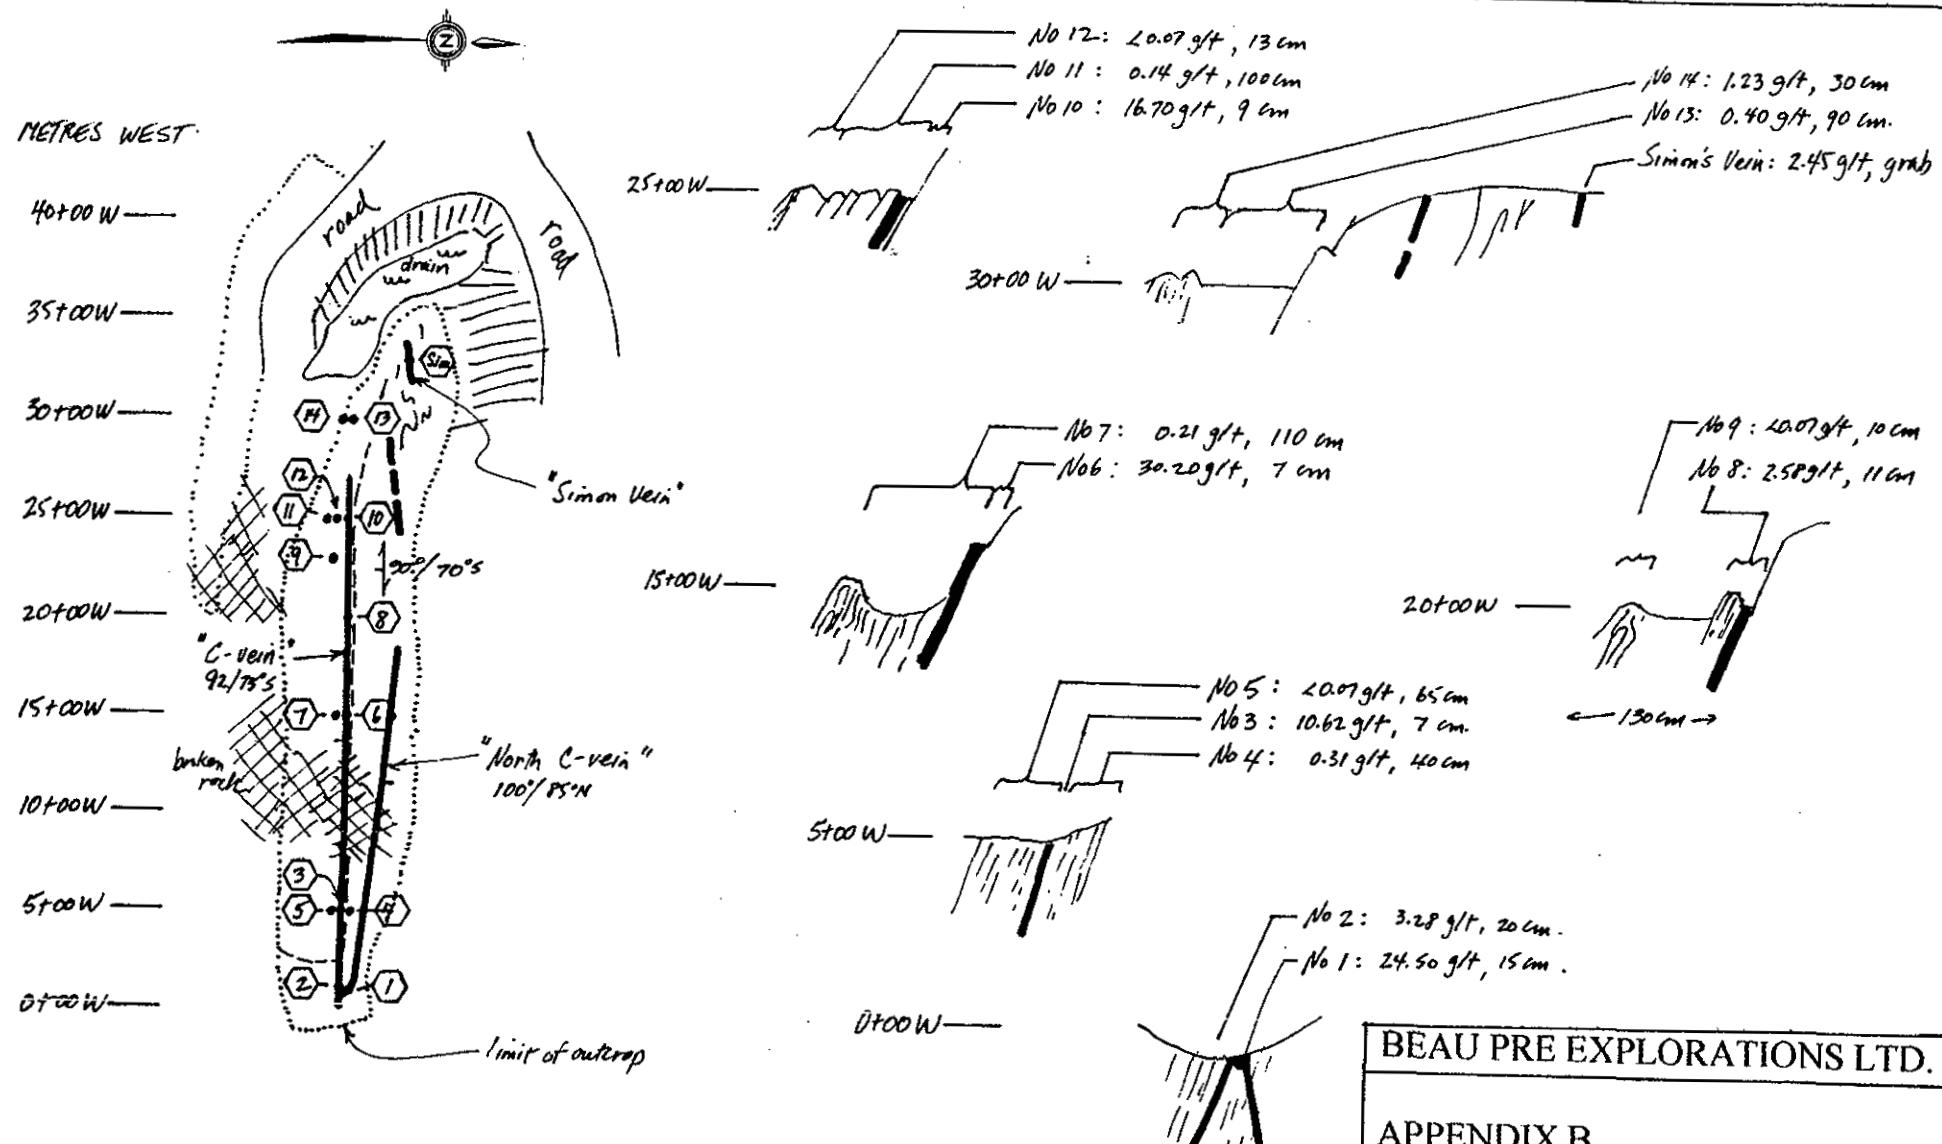

BEAU PRE EXPLORATIONS LTD.

APPENDIX B
FAIRBANK ENGINEERING LTD.
'C' TRENCH ASSAY PLAN WITH
SECTIONS, 1994

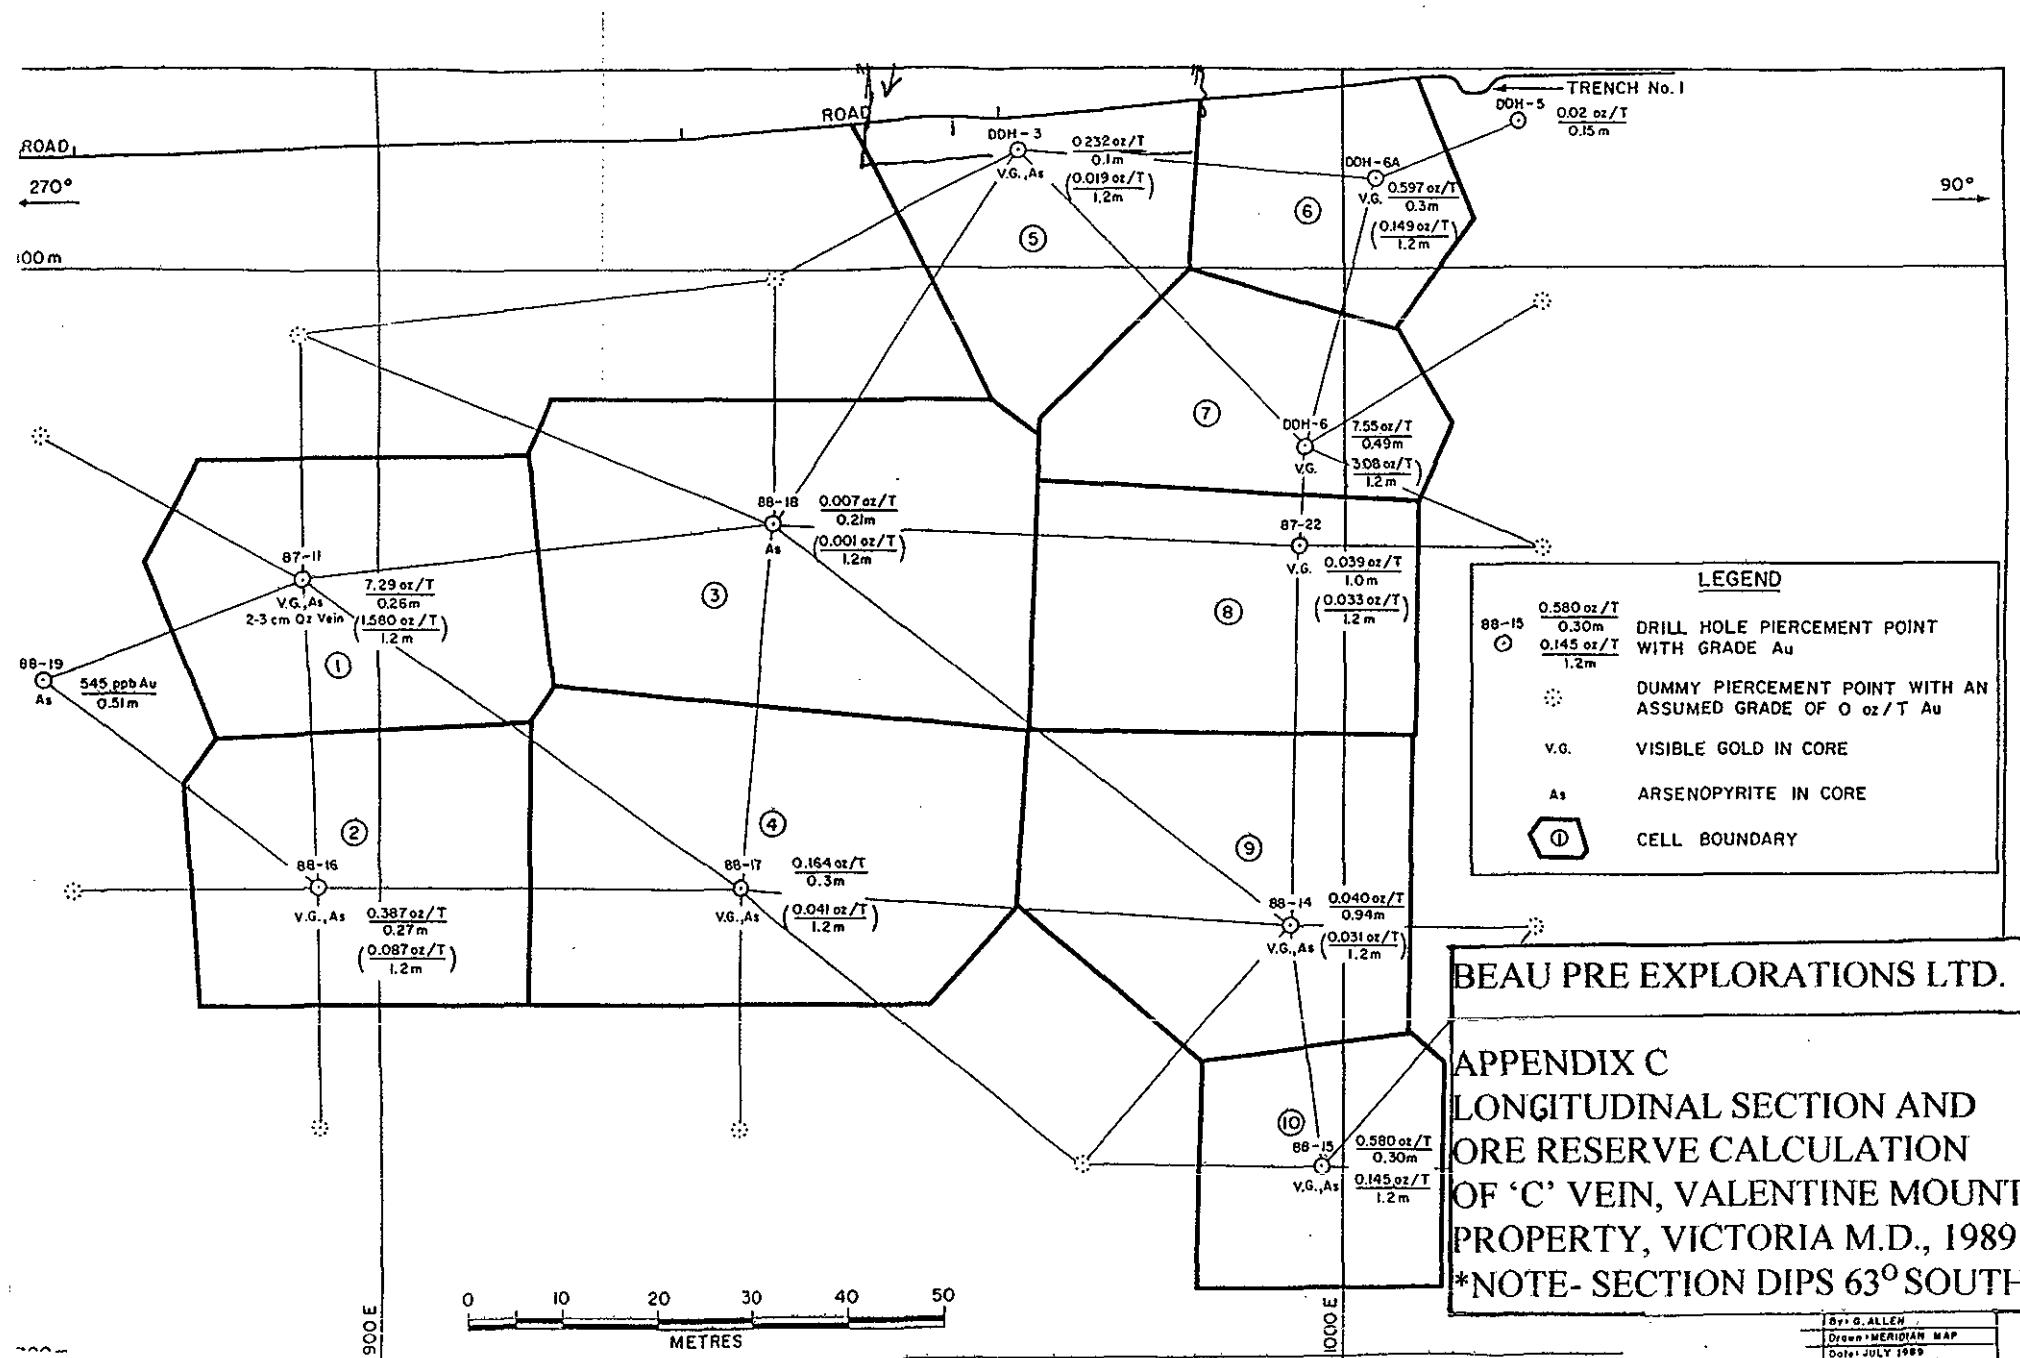

BEAU PRE EXPLORATIONS LTD.

**APPENDIX C
LONGITUDINAL SECTION AND
ORE RESERVE CALCULATION
OF 'C' VEIN, VALENTINE MOUNTAIN
PROPERTY, VICTORIA M.D., 1989
*NOTE- SECTION DIPS 63° SOUTH**

By G. ALLEN
Drawn > MERIDIAN MAP
Date: JULY 1969

VALENTINE MOUNTAIN PROPERTY
Beaupre Explorations Ltd.,
108-3980 Shelbourne St., Victoria, B.C. V8P 5P6

APPENDIX D

DRILL LOG

Hole No.: DDH 00-01

| | | | |
|------------------|--------------------------------------|--------------|----------------|
| Date Started: | December 17, 2000 | Project: | Valentine Au |
| Dated Completed: | December 17, 2000 | N.T.S.: | 92 B/12 |
| COLLAR: Pad 1 | Depth | Location: | Blaze 1 |
| Northing: | 9+90 N | | |
| Easting: | 9+00 E | Drilling Co. | Neill's Mining |
| Azimuth: | 180 | Hole type: | Diamond Drill |
| Elev: | 820.0 m (2,690 feet) above sea level | Date Logged: | Dec. 18, 2000 |
| Core Size: | BQ | Logged By: | Andris Kikauka |

| From
ft | To
ft | Recov | Description | interval in
feet | Width
feet | No. | Ounces/
ton Au |
|------------|-------------|-------|---|---------------------|---------------|--------|-------------------|
| 0.0 | 2.0 | 80 % | Rubble, oxidized biotite gneiss | | | | |
| 2.0 | 45.5 | 99 % | Biotite gneiss (metasandstone unit 2)
wood grain texture, well developed
foliation and banding @ 0-25° to core
axis, average foliation 12° to core axis,
1-5% qtz as 0.1-2.0 cm wide veins ,
buck texture qtz-chlorite veining at
24.1-24.9 ft, 28.5-30.0 ft, 36.1-37.2 ft.
cutting core axis at 40-70° to core axis | | | | |
| | | | 2.0-11.7 ft. 5% qtz as veins 10° to core
axis, weak ribbon texture | 2.0-7.0 | 5.0 | 232301 | 0.005 |
| | | | 2.0-17.0 ft. weak to moderate
parasitic Z folds in wall rock, 3-5%
pyrite as fracture fillings | 7.0-12.0 | 5.0 | 232302 | 0.005 |
| | | | same as above | 12.0-17.0 | 5.0 | 232303 | 0.005 |
| | | | Buck texture qtz vein 24.1-24.9 ft.,
3% chlorite as partings, 2% pyrite | 17.0-22.0 | 5.0 | 232304 | 0.005 |
| | | | qtz veinlets 0.1-1.0 cm 20° to core
axis | 22.0-27.0 | 5.0 | 232305 | 0.005 |
| | | | Buck texture qtz vein 28.5-30.0 ft.
1% chlorite as partings | 27.0-32.0 | 5.0 | 232306 | 0.005 |
| | | | Buck texture qtz vein 36.1-37.2 ft.
40° to core axis | 32.0-37.0 | 5.0 | 232307 | 0.005 |
| | 45.5
EOH | | 1 % qtz as veinlets 0.5 cm wide, 1 %
pyrite as fracture filling | 37.0-42.0 | 5.0 | 232308 | 0.005 |

VALENTINE MOUNTAIN PROPERTY

DRILL LOG

Beaupre Explorations Ltd.,
108-3980 Shelbourne St., Victoria, B.C. V8P 5P6

Hole No.: DDH 00-02

| | | | |
|--|-------------------|--------------|----------------|
| Date Started: | December 18, 2000 | Project: | Valentine Au |
| Dated Completed: | December 19, 2000 | N.T.S.: | 92 B/12 |
| COLLAR: Pad 2 | Depth | Location: | Blaze 1 |
| Northing: 9+90 N | | | |
| Easting: 8+81.7 E | 176.0 ft. | Drilling Co. | Neill's Mining |
| Azimuth: 180 | | Hole type: | Diamond Drill |
| Elev: 820.0 m (2,690 feet) above sea level | | Date Logged: | Dec. 20, 2000 |
| Core Size: BQ | | Logged By: | Andris Kikauka |

| From
ft | To
ft | Recov | Description | interval in
feet | Width
feet | No. | Ounces/
ton Au |
|------------|----------|-------|--|---------------------|---------------|--------|-------------------|
| 0.0 | 2.0 | 95 % | Oxidized biotite gneiss, tr. limonite | | | | |
| 2.0 | 176.0 | 99 % | Biotite gneiss (metasandstone unit 2)
wood grain texture, well developed
foliation and banding @ 0-25° to core
axis, average foliation 20° to core axis,
1-5% qtz as 0.1-2.0 cm wide veins ,
buck texture qtz-chlorite veining
cutting core axis at 40-70° to core axis
1-12 ft. wide bands of folded country
rock, minor chlorite, muscovite,
andalusite and K-spar adjacent to
qtz vein zones, main zones of qtz 0.0-
60.0 ft and 117.0-176.0 ft. qtz occurs
as 0.1-6.0 cm wide veins, sharp
contacts, milky and translucent,
anhedral texture 10-70° to core axis | | | | |
| | | | 5% qtz as veins 10-30° to core axis,
limonite chlorite, foliation at 60-80°
to core axis | 0.0-5.0 | 5.0 | 232309 | 0.005 |
| | | | 5.2-5.9 ft. buck qtz chlorite
muscovite, 3-5% pyrite as fracture
fillings | 5.0-10.0 | 5.0 | 232310 | 0.005 |
| | | | 3-5% qtz as 1-4 cm. wide veins,
minor limonite | 10.0-15.0 | 5.0 | 232311 | 0.005 |
| | | | Bleach grey wall rock, foliation at 22°
to core axis, 3% chlorite as partings,
1% pyrite | 15.0-20.0 | 5.0 | 232312 | 0.005 |
| | | | 2% qtz as veinlets 0.1-1.0 cm 20-40°
to core axis | 20.0-25.0 | 5.0 | 232313 | 0.005 |
| | | | same as above | 25.0-30.0 | 5.0 | 232314 | 0.005 |

| | | | | | | |
|-----------------------|--|--|-------------|-----|--------|-------|
| DDH
00-02
cont. | | | | | | |
| | | 2% qtz as 0.1-1.0 cm wide veins 10° to core axis | 30.0-35.0 | 5.0 | 232315 | 0.005 |
| | | 1 % qtz as veinlets 0.5 cm wide, 4 % pyrite as fracture filling | 35.0-40.0 | 5.0 | 232316 | 0.005 |
| | | same as above | 40.0-45.0 | 5.0 | 232317 | 0.005 |
| | | 2 % qtz as veinlets 0.1-0.5 cm. wide, 3 % pyrite along fractures | 45.0-50.0 | 5.0 | 232318 | 0.005 |
| | | same as above | 50.0-55.0 | 5.0 | 232319 | 0.005 |
| | | 3% qtz as veinlets 0.1-1.0 cm. wide | 55.0-60.0 | 5.0 | 232320 | 0.005 |
| | | 3% qtz as veinlets, 120.0-120.2 ft. a 3.5 cm. wide buck qtz vein at 30° to core axis | 117.0-121.5 | 4.5 | 232321 | 0.005 |
| | | 8 % qtz as veins 1.0-4.0 cm. wide at 0-30° to core axis | 121.5-126.0 | 4.5 | 232322 | 0.005 |
| | | 4% qtz as veinlets, ptygmatic folding | 126.0-130.5 | 4.5 | 232323 | 0.005 |
| | | 2% qtz as veinlets | 130.5-135.0 | 4.5 | 232324 | 0.005 |
| | | 2% qtz as veinlets | 135.0-140.0 | 5.0 | 232325 | 0.005 |
| | | 4% qtz as veinlets | 140.0-145.0 | 5.0 | 232326 | 0.005 |
| | | 8% qtz as veinlets | 145.0-150.0 | 5.0 | 232327 | 0.005 |
| | | 3% qtz as veinlets at 20-70° to core axis | 150.0-155.0 | 5.0 | 232328 | 0.005 |
| | | 8% qtz as veinlets, 10-75° to core axis | 155.0-160.0 | 5.0 | 232329 | 0.005 |
| | | 5% qtz as veinlets, 20-70° to core axis | 160.0-165.0 | 5.0 | 232330 | 0.005 |
| | | 3% qtz as veinlets, 20-55° to core axis | 165.0-170.0 | 5.0 | 232331 | 0.005 |
| | | same as above | 170.0-176.0 | 5.0 | 232332 | 0.005 |
| 176.0 | | EOH | | | | |

VALENTINE MOUNTAIN PROPERTY

DRILL LOG

Beaupre Explorations Ltd.,
108-3980 Shelbourne St., Victoria, B.C. V8P 5P6

Hole No.: DDH 00-03

| | | | | | | | |
|------------------|--------------------------------------|----------|-----------|--------------|----------------|--|--|
| Date Started: | December 20, 2000 | | | Project: | Valentine Au | | |
| Dated Completed: | December 21, 2000 | | | N.T.S.: | 92 B/12 | | |
| COLLAR: | Pad 3 | Depth | Dip Angle | Location: | Blaze 1 | | |
| Northing: | 9+98 N | | | | | | |
| Easting: | 8+63.4 E | 91.0 ft. | -55° | Drilling Co. | Neill's Mining | | |
| Azimuth: | 180 | | | Hole type: | Diamond Drill | | |
| Elev: | 818.0 m (2,684 feet) above sea level | | | Date Logged: | Dec. 22, 2000 | | |
| Core Size: | BQ | | | Logged By: | Andris Kikauka | | |

| From
ft | To
ft | Recov | Description | interval in
feet | Width
feet | No. | Ounces/
ton Au |
|------------|----------|-------|--|---------------------|---------------|--------|-------------------|
| 0.0 | 2.0 | 90 % | Rubble, oxidized biotite gneiss | | | | |
| 2.0 | 91.0 | 99 % | Biotite gneiss (metasandstone unit 2)
wood grain texture, well developed
foliation and banding @ 0-50° to core
axis, average foliation 18° to core axis,
1-20% qtz as 0.1-20.0 cm wide veins
as ribbon and buck texture qtz.
minor chlorite, trace-5% pyrite as
fracture filling and blebs, trace-0.2 %
arsenopyrite as disseminations
streaks, and blebs | | | | |
| | | | 5% qtz as 0.1-1.5 cm veins 10-40° to
core axis | 9.0-14.8 | 5.8 | 232333 | 0.005 |
| | | 90% | Fault zone, intact qtz vein at 15.0-
15.9 ft. 1-3% pyrite as fracture
fillings, muscovite, sericite | 14.8-19.9 | 5.1 | 232334 | 0.005 |
| | | 99% | 1.0-2.0 cm wide qtz veinlets at 35° to
core axis, weak fault zone 22.0-23.0 ft | 19.9-25.0 | 5.1 | 232335 | 0.005 |
| | | | 0.1-1.0 cm wide qtz veinlets, 1%
chlorite as partings, 2% pyrite, trace
arsenopyrite | 25.0-34.0 | 9.0 | 232336 | 0.005 |
| | | | qtz vein at 42° to core axis, minor
limonite, trace pyrite and
arsenopyrite | 34.0-34.8 | 0.8 | 232337 | 0.094 |
| | | | 3% qtz as veinlets, 1% chlorite as
partings | 34.8-40.0 | 5.2 | 232338 | 0.005 |

| | | | | | | |
|-----------------------|--|--|-----------|-----|--------|-------|
| DDH
00-03
cont. | | | | | | |
| | | 3% qtz as veinlets 40° to core axis | 40.0-44.5 | 4.5 | 232339 | 0.005 |
| | | same as above | 44.5-49.0 | 4.5 | 232340 | 0.005 |
| | | 50% qtz as veins to 20.0 cm, trace pyrite arsenopyrite | 49.0-52.3 | 3.3 | 232341 | 0.005 |
| | | 15% qtz as veinlets and veins to 5.0 cm., minor chlorite, trace-4% pyrite | 52.3-57.6 | 5.3 | 232342 | 0.005 |
| | | quartz vein, swirled translucent milky colour, minor chlorite, trace pyrite, arsenopyrite, qtz vein forms sharp contacts at 38° to core axis | 57.6-59.7 | 2.1 | 232343 | 0.005 |
| | | 3% qtz as veinlets | 59.7-64.6 | 4.9 | 232344 | 0.005 |
| | | 8% qtz as veinlets to 2.0 cm. wide, at 50° to core axis | 74.8-79.8 | 5.0 | 232345 | 0.116 |
| | | quartz vein, minor fragments and partings of wall rock, translucent and milky quartz cuts country rock at 30-50° to core axis | 79.8-82.0 | 2.2 | 232346 | 0.005 |
| | | 5% qtz as veinlets | | | | |
| | | 91.0 ft. EOH | | | | |

VALENTINE MOUNTAIN PROPERTY

DRILL LOG

Beaupre Explorations Ltd.,
108-3980 Sheilbourne St., Victoria, B.C. V8P 5P6

Hole No.: 00-04

Date Started: December 23, 2000
 Dated Completed: December 23, 2000
 COLLAR: Pad 4 Depth Dip Angle
 Northing: 9+97 N Depth Dip Angle
 Easting: 8+81.7 E 31.0 ft. -60°
 Azimuth: 000
 Elev: 819.0 m (2,687 feet) above sea level
 Core Size: BQ

Project: Valentine Au
 N.T.S.: 92 B/12
 Location: Blaze 1
 Drilling Co.: Neill's Mining
 Hole type: Diamond Drill
 Date Logged: Dec. 23, 2000
 Logged By: Andris Kikauka

| From ft | To ft | Recov | Description | interval in feet | Width feet | No. | Ounces/ton Au |
|---------|-------|-------|---|------------------|------------|--------|---------------|
| 0.0 | 2.0 | 90 % | Rubble, oxidized biotite gneiss | | | | |
| 2.0 | 45.5 | 99 % | Biotite gneiss (metasandstone unit 2)
wood grain texture, well developed foliation and banding @ 50-75° to core axis, average foliation 12° to core axis, 1-5% qtz as 0.1-2.0 cm wide veins , buck texture qtz-chlorite veining cutting core axis at 30-70° to core axis | | | | |
| | | | qtz as 1-11.0 cm. wide veins 40-60° to core axis, foliation at 70° to core axis | 3.0-6.3 | 3.3 | 232347 | 0.005 |
| | | | quartz vein at 38° to core axis, 2% chlorite, 1 % pyrite | 13.1-14.0 | 0.9 | 232348 | 0.005 |
| | | | 0.1-1.0 cm qtz veins at 35° to core axis | 14.0-19.8 | 4.8 | 232349 | 0.005 |
| | | | 12.0 cm wide quartz vein with oxidized (limonitic) upper contact, banded quartz along lower contact | 19.8-20.3 | 0.5 | 232350 | 0.005 |
| | | | 31.0 ft. EOH | | | | |

VALENTINE MOUNTAIN PROPERTY
Beaupre Explorations Ltd.,
108-3980 Shelbourne St., Victoria, B.C. V8P 5P6

DRILL LOG

Hole No.: 00-05

| | | | |
|------------------|--------------------------------------|---------------|----------------|
| Date Started: | December 24, 2000 | Project: | Valentine Au |
| Dated Completed: | December 24, 2000 | N.T.S.: | 92 B/12 |
| COLLAR: Pad 4 | Depth | Location: | Blaze 1 |
| Northing: | 9+97 N | | |
| Easting: | 8+81.7 E | Drilling Co.: | Neill's Mining |
| Azimuth: | 180 | Hole type: | Diamond Drill |
| Elev: | 819.0 m (2,687 feet) above sea level | Date Logged: | Dec. 24 2000 |
| Core Size: | BQ | Logged By: | Andris Kikauka |

| From ft | To ft | Recov | Description | interval in feet | Width feet | No. | Ounces/ton Au |
|---------|-------|-------|---|------------------|------------|--------|---------------|
| 0.0 | 1.0 | 95 % | Rubble, oxidized biotite gneiss | | | | |
| 1.0 | 50.0 | 99 % | Biotite gneiss (metasandstone unit 2)
wood grain texture, well developed foliation and banding @ 30-55° to core axis, average foliation 42° to core axis, 1-5% qtz as 0.1-2.0 cm wide veins , buck texture qtz-chlorite veining cutting core axis at 30-70° to core axis | | | | |
| | | | 8% qtz as 1.0-4.0 cm veinlets 30-50° to core axis, foliation at 40° to core axis | 0.0-3.0 | 3.0 | 232352 | 0.005 |
| | | | 3% qtz as veinlets, foliation at 35-55° to core axis | 3.0-7.2 | 4.2 | 232353 | 0.005 |
| | | | same as above | 7.2-11.7 | 4.5 | 232354 | 0.005 |
| | | | 6% qtz as veins at 35-65° to core axis, 3% chlorite as partings, 2% pyrite | 11.7-16.2 | 4.5 | 232355 | 0.005 |
| | | | qtz veinlets 0.1-1.0 cm 40° to core axis | 26.5-31.2 | 4.7 | 232356 | 0.005 |
| | | | 5% qtz as veins, 1% chlorite as partings, qtz veins at 38° to core axis | 31.2-35.0 | 3.8 | 232357 | 0.005 |
| | | | 2% qtz as veinlets, foliation at 50° to core axis | 35.0-43.2 | 8.2 | 232358 | 0.005 |
| | | 94% | Fault zone, quartz vein, 5% chlorite as light green colour partings, trace pyrite | 43.2-44.7 | 1.5 | 232359 | 0.005 |

| | | | | | | | |
|-----------------------|--|-----|---|-----------|-----|--------|-------|
| DDH
00-05
cont. | | | | | | | |
| | | 92% | Fault zone, 3% qtz as veins, 1% chlorite as partings, qtz veins at 18° to core axis | 44.7-50.0 | 5.3 | 232360 | 0.005 |
| | | | 50.0 ft. EOH | | | | |

VALENTINE MOUNTAIN PROPERTY

**Beaupre Explorations Ltd.,
108-3980 Shelbourne St., Victoria, B.C. V8P 5P6**

DRILL LOG

Hole No.: 00-06

Date Started: December 27, 2000

Dated Completed: December 28, 2000

COLLAR: Pad 5

Northing: 9+91 N

Easting: 8+87.8 E

Azimuth: 180

Elev: 819.0 m

Core Size: BQ

Core size: BQ

Project: Valentine Au

N.T.S.:

92 B/12

Location: Blaze 1

Drilling Co., Neill's Mining

Hole type: Diamond Drill

Hole type: Diamond D
Date Logged: Dec. 29 2000

Date Logged: Dec. 29 2000

| | | | | | | |
|-----------------------|--|--|-------------|-----|--------|-------|
| DDH
00-06
cont. | | | | | | |
| | | qtz veinlets 0.1-1.0 cm 40° to core axis | 14.5-21.5 | 4.7 | 232405 | 0.005 |
| | | 5% qtz as veins, 1% chlorite as partings, qtz veins at 10-30° to core axis | 21.5-26.2 | 4.7 | 232406 | 0.005 |
| | | 3% qtz as veinlets, foliation at 20-40° to core axis | 26.2-31.0 | 4.8 | 232407 | 0.005 |
| | | 8% quartz as veins, 5% chlorite as light green colour partings, trace pyrite, foliation 5-20° to core axis | 66.9-72.0 | 5.1 | 232408 | 0.005 |
| | | 15% qtz @10-60° to core axis, foliation @10-20° to core axis | 72.0-77.0 | 5.0 | 232409 | 0.005 |
| | | 3% qtz as veins 25-55° to core axis | 77.0-82.5 | 5.5 | 232410 | 0.005 |
| | | 30% qtz as 1-35 cm wide veins | 82.5-88.0 | 5.5 | 232411 | 0.005 |
| | | 5% qtz, foliation @10° to core axis | 88.0-93.5 | 5.5 | 232412 | 0.005 |
| | | qtz vein at 10-70° to core axis, sharp convoluted contact | 93.5-98.0 | 4.5 | 232413 | 0.005 |
| | | 30% qtz as 30 cm wide vein, minor chlorite, pyrite, trace arsenopyrite | 98.0-102.2 | 4.2 | 232414 | 0.005 |
| | | 20% qtz as veins @5-80° to core axis | 102.3-107.0 | 4.7 | 232415 | 0.005 |
| | | 8% qtz | 107.0-111.0 | 4.0 | 232416 | 0.005 |
| | | 3% qtz as veins @25-55° to core axis | 111.0-118.0 | 7.0 | 232417 | 0.005 |

VALENTINE MOUNTAIN PROPERTY

DRILL LOG

Beupre Explorations Ltd.,

108-3980 Shelbourne St., Victoria, B.C. V8P 5P6

Hole No.: 00-07

Date Started: December 28, 2000

Project: Valentine Au

Dated Completed: December 29, 2000

N.T.S.: 92 B/12

COLLAR: Pad 6

Depth

Dip Angle

Location: Blaze 1

Northing: 10+05 N

Easting: 9+18.7 E

34.0 ft.

-60°

Drilling Co. Neill's Mining

Azimuth: 000

Hole type: Diamond Drill

Elev: 818.0 m (2,684 feet) above sea level

Date Logged: Dec. 29 2000

Core Size: BQ

Logged By: Andris Kikauka

| From
ft | To
ft | Recov | Description | interval in
feet | Width
feet | No. | Ounces/
ton Au |
|------------|-------------|-------|---|---------------------|---------------|--------|-------------------|
| 0.0 | 1.0 | 95 % | Rubble, oxidized biotite gneiss | | | | |
| 1.0 | 34.0 | 99 % | Biotite gneiss (metasandstone unit 2)
wood grain texture, well developed
foliation and banding @ 20-65° to
core axis, average foliation 40° to core
axis, 1-5% qtz as 0.1-2.0 cm wide
veins , buck texture qtz-chlorite
veining cutting core axis at 10-70° to
core axis | | | | |
| | | | qtz vein, weak vuggy texture, sharp
contact @40-70° to core axis, foliation
at 40° to core axis, 3% limonite | 10.4-12.9 | 2.5 | 232421 | 0.005 |
| | 34.0
EOH | | same as above | 12.9-15.4 | 2.5 | 232422 | 0.005 |

VALENTINE MOUNTAIN PROPERTY

DRILL
LOG

Beaupre Explorations Ltd.,
108-3980 Shelbourne St., Victoria, B.C. V8P 5P6

Hole No.: 00-03

| | | | | | |
|------------------|--------------------------------------|----------|-----------|---------------|----------------|
| Date Started: | December 30, 2000 | | Project: | Valentine Au | |
| Dated Completed: | December 31, 2000 | | N.T.S.: | 92 B/12 | |
| COLLAR: | Pad 6 | Depth | Dip Angle | Location: | Blaze 1 |
| Northing: | 10+05 N | | | | |
| Easting: | 9+18.7 E | 53.5 ft. | -60° | Drilling Co.: | Neill's Mining |
| Azimuth: | 030 | | | Hole type: | Diamond Drill |
| Elev: | 818.0 m (2,684 feet) above sea level | | | Date Logged: | Dec. 30, 2000 |
| Core Size: | BQ | | | Logged By: | Andris Kikauka |

| From
ft | To
ft | Recov | Description | interval in
feet | Width
feet | No. | Ounces/
ton Au |
|------------|-------------|-------|---|---------------------|---------------|--------|-------------------|
| 0.0 | 1.0 | 95 % | Rubble, oxidized biotite gneiss | | | | |
| 1.0 | 53.5 | 99 % | Biotite gneiss (metasandstone unit 2)
wood grain texture, well developed
foliation and banding @ 20-75° to
core axis, average foliation 50° to core
axis, 1-5% qtz as 0.1-2.0 cm wide
veins , buck texture qtz-chlorite
veining cutting core axis at 20-70° to
core axis | | | | |
| | | | qtz vein, weak vuggy texture, sharp
contact @50-80° to core axis, foliation
at 40° to core axis, 3% limonite | 9.3-11.8 | 2.5 | 232418 | 0.005 |
| | | | same as above | 11.8-14.3 | 2.5 | 232419 | 0.005 |
| | 53.5
EOH | | 20% qtz as 1-2 cm wide veins,
chlorite, pyrite, foliation @35-65° to
core axis | 39.3-47.7 | 8.4 | 232420 | 0.005 |

Geo-facts

4-6 4901 East Sooke Rd, Sooke, B.C.
V0S 1N0

DRILL HOLE DESCRIPTION DETAILED GRAPHIC LOG

Project: *Valentine* APPENDIX E

*NOTE - All distance
measurements are
given in meters

Hole #: 00-01

Comments: Competent coring throughout, excellent recovery

Northing: 990.000
Easting: 900.000
Elevation: 820.000
Field Location: Discovery trench, 'C'

Casing Exposed: 0.0
Casing Size: BQ
Contractor: Neill's Mining
Assay Lab: Bondar-Clegg

Dip Tests
Hole # Depth Azimuth Dip
00-01 0.00 180.00 -68.00

Length: 13.90
Start Dip: -68.0
Start Azimuth: 180

Project: Valentine
Area: Near mill
Property: Beaupre Explorations Ltd

Logged by: A.Kikauka
Log date: 18/12/2000
Date Started: 17/12/2000
Date Finished: 17/12/2000

Map Reference: 92 B\12
Claim: Blaze 1
Region: Victoria Mining



| Hole ID: 00-01 | | | Geo-facts | | | chl | Project: Valentine | | | | | | |
|----------------|-------|--|-----------|----|-----|-----|--------------------|-------|-------|--------|--------|--------|------|
| From | To | Description | qtz | py | chl | | From | To | Width | Sample | Au OPT | Ag OPT | As % |
| 0.00 | 13.90 | Biotite gneiss | | | | | 0.61 | 2.14 | 1.53 | 232301 | 0.005 | 0.05 | 0.01 |
| | | Wood grain texture, foliation and banding 0-25 degrees to core axis | | | | | | | | | | | |
| | | qtz 1.00-5.00% chl 1.00-3.00% quartz veining 7.35-7.6, 8.7-9.15,
and 11.0-11.35 | | | | | 2.14 | 3.67 | 1.53 | 232302 | 0.005 | 0.05 | 0.01 |
| | | | | | | | 3.67 | 5.20 | 1.53 | 232303 | 0.005 | 0.05 | 0.01 |
| | | | | | | | 5.20 | 6.71 | 1.51 | 232304 | 0.005 | 0.05 | 0.01 |
| | | | | | | | 6.71 | 8.22 | 1.51 | 232305 | 0.005 | 0.05 | 0.04 |
| | | | | | | | 8.22 | 9.73 | 1.51 | 232306 | 0.005 | 0.05 | 0.01 |
| | | | | | | | 9.73 | 11.29 | 1.56 | 232307 | 0.005 | 0.05 | 0.01 |
| | | | | | | | 11.29 | 12.81 | 1.52 | 232308 | 0.005 | 0.05 | 0.01 |

Geo-facts

4-6 4901 East Sooke Rd, Sooke, B.C.
V0S 1N0

**DRILL HOLE DESCRIPTION
DETAILED GRAPHIC LOG**

Project: *Valentine*

Hole #: 00-02

Comments: Competent coring throughout, excellent recovery

Northing: 990.000
Easting: 881.700
Elevation: 820.000
Field Location: Discovery trench, 'C'

Casing Exposed: 0.0
Casing Size: BQ
Contractor: Neill's Mining
Assay Lab: Bondar-Clegg

Dip Tests

| Hole # | Depth | Azimuth | Dip |
|--------|-------|---------|--------|
| 00-02 | 0.00 | 180.00 | -68.00 |

Length: 53.68
Start Dip: -68.0
Start Azimuth: 180

Project: Valentine
Area: Near mill
Property: Beaupre Explorations Ltd

Logged by: A.Kikauka
Log date: 20/12/2000
Date Started: 18/12/2000
Date Finished: 19/12/2000

Map Reference: 92 B12
Claim: Blaze 1
Region: Victoria Mining

| Geo-facts | | | chl | Project: Valentine | | | | | | |
|-----------|----|-------------|-----|--------------------|-------|-------|--------|--------|--------|------|
| From | To | Description | chl | From | To | Width | Sample | Au OPT | Ag OPT | As % |
| qtz | py | | 1 | | | | | | | |
| | | | | 35.00 | | | | | | |
| | | | | 35.68 | 37.05 | 1.37 | 232321 | 0.005 | 0.05 | 0.01 |
| | | | | 37.05 | 38.42 | 1.37 | 232322 | 0.005 | 0.06 | 0.01 |
| | | | | 38.42 | 39.79 | 1.37 | 232323 | 0.005 | 0.05 | 0.01 |
| | | | | 39.79 | 41.16 | 1.37 | 232324 | 0.005 | 0.05 | 0.01 |
| | | | | 41.16 | 42.70 | 1.54 | 232325 | 0.005 | 0.05 | 0.01 |
| | | | | 42.70 | 44.23 | 1.53 | 232326 | 0.005 | 0.05 | 0.01 |
| | | | | 44.23 | 45.76 | 1.53 | 232327 | 0.005 | 0.05 | 0.01 |
| | | | | 45.76 | 47.29 | 1.53 | 232328 | 0.005 | 0.05 | 0.01 |
| | | | | 47.29 | 48.82 | 1.53 | 232329 | 0.005 | 0.05 | 0.01 |
| | | | | 48.82 | 50.35 | 1.53 | 232330 | 0.005 | 0.05 | 0.01 |
| | | | | 50.35 | 51.88 | 1.53 | 232331 | 0.005 | 0.05 | 0.01 |
| | | | | 51.88 | 53.68 | 1.80 | 232332 | 0.005 | 0.13 | 0.01 |

Geo-facts

4-6 4901 East Sooke Rd, Sooke, B.C.
V0S 1N0

**DRILL HOLE DESCRIPTION
DETAILED GRAPHIC LOG**

Project: *Valentine*

Hole #: 00-03

Comments: Competent coring throughout, excellent recovery

Northing: 998.000
Easting: 863.400
Elevation: 818.000
Field Location: Discovery trench, 'C'

Casing Exposed: 0.0
Casing Size: BQ
Contractor: Neill's Mining
Assay Lab: Bondar-Clegg

Length: 27.75
Start Dip: -55.0
Start Azimuth: 180

Project: Valentine
Area: Near mill
Property: Beaupre Explorations Ltd

Logged by: A.Kikauka
Log date: 22/12/2000
Date Started: 20/12/2000
Date Finished: 21/12/2000

Map Reference: 92 B\12
Claim: Blaze 1
Region: Victoria Mining

Dip Tests

| Hole # | Depth | Azimuth | Dip |
|--------|-------|---------|--------|
| 00-03 | 0.00 | 180.00 | -55.00 |



Hole ID: 00-03

Geo-facts

chl

Project: Valentine

From To Description

qtz py chl

From To Width Sample Au OPT Ag OPT As %

0.00 - 27.75 Biotite gneiss

Wood grain texture, foliation and banding 0-50 degrees to core axis,
 qtz 1.00-20.00% quartz occurs as 0.1-20.0 cm wide veins as ribbon and
 buck texture, chl 1.00-5.00% py 0.10-5.00%

5.00

10.00

15.00

20.00

25.00

2.74 4.51 1.77 232333 0.005 0.05 0.01

4.51 6.07 1.56 232334 0.005 0.05 0.01

6.07 7.63 1.56 232335 0.005 0.05 0.01

7.63 10.37 2.74 232336 0.005 0.05 0.01

10.37 10.61 0.24 232337 0.094 0.05 0.07

10.61 12.20 1.59 232338 0.005 0.05 0.01

12.20 13.57 1.37 232339 0.005 0.05 0.01

13.57 14.94 1.37 232340 0.005 0.05 0.01

14.94 15.95 1.01 232341 0.005 0.05 0.01

15.95 17.57 1.62 232342 0.005 0.05 0.01

17.57 18.21 0.64 232343 0.005 0.05 0.01

18.21 19.70 1.49 232344 0.005 0.05 0.01

22.81 24.34 1.53 232345 0.116 0.05 0.34

24.34 25.01 0.67 232346 0.005 0.13 0.08

Geo-facts

4-6 4901 East Sooke Rd, Sooke, B.C.
V0S 1N0

**DRILL HOLE DESCRIPTION
DETAILED GRAPHIC LOG****Project: Valentine****Hole #:** 00-04**Comments:** Competent coring throughout, excellent recovery

Northing: 997.000
Easting: 881.700
Elevation: 819.000
Field Location:Discovery trench, 'B'

Casing Exposed: 0.0
Casing Size: BQ
Contractor: Neill's Mining
Assay Lab: Bondar-Clegg

Dip Tests
Hole # Depth Azimuth Dip
00-04 0.00 0.00 -60.00

Length: 9.46
Start Dip: -60.0
Start Azimuth: 0

Project: Valentine
Area: Near mill
Property: Beaupre Explorations Ltd

Logged by: A.Kikauka
Log date: 23/12/2000
Date Started: 23/12/2000
Date Finished: 24/12/2000

Map Reference: 92 B\12
Claim: Blaze 1
Region: Victoria Mining

Geo-facts

4-6 4901 East Sooke Rd, Sooke, B.C.
V0S 1N0

**DRILL HOLE DESCRIPTION
DETAILED GRAPHIC LOG**

Project: *Valentine*

Hole #: 00-05

Comments: Competent coring throughout, excellent recovery

Northing: 997.000
Easting: 881.700
Elevation: 819.000
Field Location: Discovery trench, 'B'

Casing Exposed: 0.0
Casing Size: BQ
Contractor: Neill's Mining
Assay Lab: Bondar-Clegg

Dip Tests

| Hole # | Depth | Azimuth | Dip |
|--------|-------|---------|--------|
| 00-05 | 0.00 | 0.00 | -60.00 |

Length: 15.25
Start Dip: -90.0
Start Azimuth: 0

Project: Valentine
Area: Near mill
Property: Beaupre Explorations Ltd

Logged by: A.Kikauka
Log date: 24/12/2000
Date Started: 24/12/2000
Date Finished: 24/12/2000

Map Reference: 92 B\12
Claim: Blaze 1
Region: Victoria Mining

| Hole ID: 00-05 | | | Geo-facts | | | chl | Project: Valentine | | | | | | | | |
|----------------|-------|--|-----------|----|-----|-----|--------------------|-------|-------|--------|--------|--------|------|------|--|
| From | To | Description | qtz | py | chl | | From | To | Width | Sample | Au OPT | Ag OPT | As % | | |
| 0.00 - | 15.25 | Biotite gneiss | | | | | | 0.92 | 0.92 | 1.27 | 232352 | 0.005 | 0.05 | 0.01 | |
| | | Wood grain texture, foliation and banding 30-55 degrees to core axis | | | | | 0.92 | 2.19 | 1.27 | 232353 | 0.005 | 0.05 | 0.01 | | |
| | | qtz 1.00-5.00% chl 1.00-3.00% py 0.20-0.50% quartz-chlorite vein | | | | | 2.19 | 3.57 | 1.38 | 232354 | 0.005 | 0.05 | 0.01 | | |
| | | 0.0-0.92, 9.52-10.7, fault zone 13.2-13.63 | | | | | 3.57 | 4.95 | 1.38 | 232355 | 0.005 | 0.05 | 0.01 | | |
| | | | | | | | | | | | | | | | |
| | | | | | | | | | | | | | | | |
| | | | | | | | | 8.08 | 9.52 | 1.44 | 232356 | 0.005 | 0.05 | 0.01 | |
| | | | | | | | | 9.52 | 10.68 | 1.16 | 232357 | 0.005 | 0.05 | 0.01 | |
| | | | | | | | | 10.68 | 13.18 | 2.50 | 232358 | 0.005 | 0.05 | 0.01 | |
| | | | | | | | | 13.18 | 13.63 | 0.45 | 232359 | 0.005 | 0.10 | 0.01 | |
| | | | | | | | | 13.63 | 15.25 | 1.62 | 232360 | 0.005 | 0.05 | 0.01 | |
| | | | | | | | | | | | | | | | |

Geo-facts

4-6 4901 East Sooke Rd, Sooke, B.C.
V0S 1N0

**DRILL HOLE DESCRIPTION
DETAILED GRAPHIC LOG**

Project: *Valentine*

Hole #: 00-06

Comments: Competent coring throughout, excellent recovery

| | |
|-----------------|-----------------------|
| Northing: | 991.000 |
| Easting: | 887.800 |
| Elevation: | 819.000 |
| Field Location: | Discovery trench, 'C' |

| | |
|-----------------|----------------|
| Casing Exposed: | 0.0 |
| Casing Size: | |
| Contractor: | Neill's Mining |
| Assay Lab: | Bondar-Clegg |

| Dip Tests | | | |
|-----------|-------|---------|--------|
| Hole # | Depth | Azimuth | Dip |
| 00-06 | 0.00 | 180.00 | -60.00 |

| | |
|----------------|-------|
| Length: | 36.00 |
| Start Dip: | 0.0 |
| Start Azimuth: | 0 |

| | |
|-----------|--------------------------|
| Project: | Valentine |
| Area: | Near mill |
| Property: | Beaupre Explorations Ltd |

| | |
|----------------|------------|
| Logged by: | A.Kikauka |
| Log date: | 29/12/2000 |
| Date Started: | 27/12/2000 |
| Date Finished: | 28/12/2000 |

| | |
|----------------|-----------------|
| Map Reference: | 92 B\12 |
| Claim: | Blaze 1 |
| Region: | Victoria Mining |

| Hole ID: 00-06 | | | Geo-facts | | | chl | Project: Valentine | | | | | | |
|----------------|-------|--|-----------|----|-----|-----|--------------------|-------|-------|--------|--------|--------|------|
| From | To | Description | qtz | py | chl | | From | To | Width | Sample | Au OPT | Ag OPT | As % |
| 0.00 | 35.99 | Biotite gneiss
<i>Wood grain texture, foliation and banding 10-65 degrees to core axis</i>
qtz 1.00-5.00% chl 0.50-5.00% py 0.20-2.00% quartz vein
4.02-4.42, 20.40-21.96, 25.16-26.84, 28.52-33.85 | | | | | 0.76 | 1.49 | 0.73 | 232401 | 0.005 | 0.05 | 0.01 |
| | | | | | | | 1.49 | 2.84 | 1.35 | 232402 | 0.005 | 0.05 | 0.01 |
| | | | | | | | 2.84 | 4.03 | 1.19 | 232403 | 0.005 | 0.05 | 0.03 |
| | | | | | | | 4.03 | 4.42 | 0.39 | 232404 | 0.019 | 0.05 | 0.07 |
| | | | | | | | 4.42 | 6.56 | 2.14 | 232405 | 0.005 | 0.05 | 0.01 |
| | | | | | | | 6.56 | 7.99 | 1.43 | 232406 | 0.005 | 0.05 | 0.01 |
| | | | | | | | 7.99 | 9.46 | 1.47 | 232407 | 0.005 | 0.05 | 0.01 |
| | | | | | | | 20.40 | 21.96 | 1.56 | 232408 | 0.005 | 0.05 | 0.00 |
| | | | | | | | 21.96 | 23.49 | 1.53 | 232409 | 0.005 | 0.05 | 0.01 |
| | | | | | | | 23.49 | 25.16 | 1.67 | 232410 | 0.005 | 0.05 | 0.01 |
| | | | | | | | 25.16 | 26.83 | 1.67 | 232411 | 0.005 | 0.05 | 0.01 |
| | | | | | | | 26.83 | 28.50 | 1.67 | 232412 | 0.005 | 0.05 | 0.01 |
| | | | | | | | 28.50 | 29.89 | 1.39 | 232413 | 0.005 | 0.05 | 0.01 |
| | | | | | | | 29.89 | 31.17 | 1.28 | 232414 | 0.005 | 0.05 | 0.01 |
| | | | | | | | 31.17 | 32.64 | 1.47 | 232415 | 0.005 | 0.05 | 0.01 |
| | | | | | | | 32.64 | 33.86 | 1.22 | 232416 | 0.005 | 0.05 | 0.01 |



| Hole ID: 00-06 | | | Geo-facts | | | chl | Project: Valentine | | | | | | |
|----------------|----|-------------|-----------|----|-----|-----|--------------------|-------|-------|--------|--------|--------|------|
| From | To | Description | qtz | py | chl | chl | From | To | Width | Sample | Au OPT | Ag OPT | As % |
| | | | | | | | 33.86 | 35.99 | 2.13 | 232417 | 0.005 | 0.05 | 0.01 |

Geo-facts

4-6 4901 East Sooke Rd, Sooke, B.C.
V0S 1N0

**DRILL HOLE DESCRIPTION
DETAILED GRAPHIC LOG**

Project: Valentine

Hole #: 00-07

Comments: Competent coring throughout, excellent recovery

Northing: 1005.000
Easting: 918.700
Elevation: 818.000
Field Location: Discovery trench, 'B'

Casing Exposed: 0.0
Casing Size:
Contractor: Neill's Mining
Assay Lab: Bondar-Clegg

Dip Tests

| Hole # | Depth | Azimuth | Dip |
|--------|-------|---------|-----|
| 00-07 | 0.00 | 0.00 | -60 |

Length: 10.37
Start Dip: 0.0
Start Azimuth: 0

Project: Valentine
Area: Near mill
Property: Beaupre Explorations Ltd

Logged by: A.Kikauka
Log date: 29/12/2000
Date Started: 28/12/2000
Date Finished: 29/12/2000

Map Reference: 92 B\12
Claim: Blaze 1
Region: Victoria Mining

Geo-facts

4-6 4901 East Sooke Rd, Sooke, B.C.
V0S 1N0

**DRILL HOLE DESCRIPTION
DETAILED GRAPHIC LOG**

Project: *Valentine*

Hole #: 00-08

Comments: Competent coring throughout, excellent recovery

Northing: 1005.000
Easting: 0.000
Elevation: 818.000
Field Location: Discovery trench, 'B'

Casing Exposed: 0.0
Casing Size:
Contractor: Neill's Mining
Assay Lab: Bondar-Clegg

Length: 16.32
Start Dip: 0.0
Start Azimuth: 0

Project: Valentine
Area: Near mill
Property: Beaupre Explorations Ltd

Logged by: A.Kikauka
Log date: 30/12/2000
Date Started: 30/12/2000
Date Finished: 31/12/2000

Map Reference: 92 B12
Claim: Blaze 1
Region: Victoria Mining

Dip Tests

| Hole # | Depth | Azimuth | Dip |
|--------|-------|---------|--------|
| 00-08 | 0.00 | 0.00 | -60.00 |



BONDAR CLEGG

APPENDIX F

Vancouver, B.C. Canada

" U R G E N T & C O N F I D E N T I A L "

To: BEAU PRE EXPLORATIONS LTD.
 Attention :
 Reference :
 Submitter : UNKNOWN

Our Fax No: (604) 985-1071
 Your Fax No: 1-250-384-6431
 Number of Pages : 2 including this page.

Report : V01-00287.0 Status : COMPLETE Total number of samples: 61

| Element Method | Total | Element Method | Total | Element Method | Total |
|--------------------|-------|------------------------|-------|------------------------|-------|
| AuGrav GRAVIMETRIC | 61 | AgGrav FIRE ASSAY-GRAV | 61 | As AAS LOW LEVEL ASSAY | 61 |

| Sample Preparations | Total | Sample Type | Total | Size Fraction | Total | Remarks |
|---------------------|-------|-------------|-------|---------------|-------|---------|
|---------------------|-------|-------------|-------|---------------|-------|---------|

| | | | | | | |
|---------------------|----|------------|----|------|----|--|
| CRUSH/SPLIT & PULV. | 61 | DRILL CORE | 61 | -150 | 61 | |
|---------------------|----|------------|----|------|----|--|

| | | | | | | |
|---------------|-----|--|--|--|--|--|
| OVERWEIGHT/KG | 102 | | | | | |
|---------------|-----|--|--|--|--|--|

Notes:

If you do not receive the entire transmission in legible form, please call us at (604) 985-0681.



BONDAR CLEGG

CLIENT: BEAU PRE EXPLORATIONS LTD.

REPORT: V01-00287.0 (COMPLETE)

PROJECT: VF-2000

DATE RECEIVED: 19-FEB-01

DATE PRINTED: 24-FEB-01

PAGE 1 OF 1

| SAMPLE
NUMBER | ELEMENT
UNITS | AuGrav
OPT | AgGrav
OPT | As
PCT | SAMPLE
NUMBER | ELEMENT
UNITS | AuGrav
OPT | AgGrav
OPT | As
PCT |
|------------------|------------------|---------------|---------------|-----------|------------------|------------------|---------------|---------------|-----------|
| D2 232301 | | <0.005 | <0.05 | <0.01 | D2 232341 | | <0.005 | <0.05 | <0.01 |
| D2 232302 | | <0.005 | <0.05 | <0.01 | D2 232342 | | <0.005 | <0.05 | <0.01 |
| D2 232303 | | <0.005 | <0.05 | <0.01 | D2 232343 | | <0.005 | <0.05 | <0.01 |
| D2 232304 | | <0.005 | <0.05 | <0.01 | D2 232344 | | <0.005 | <0.05 | <0.01 |
| D2 232305 | | <0.005 | <0.05 | 0.04 | D2 232345 | | 0.116 | <0.05 | 0.34 |
| D2 232306 | | <0.005 | <0.05 | <0.01 | D2 232346 | | 0.005 | 0.13 | 0.08 |
| D2 232307 | | <0.005 | <0.05 | <0.01 | D2 232347 | | <0.005 | <0.05 | 0.04 |
| D2 232308 | | <0.005 | <0.05 | <0.01 | D2 232348 | | <0.005 | <0.05 | <0.01 |
| D2 232309 | | <0.005 | <0.05 | <0.01 | D2 232349 | | <0.005 | <0.05 | <0.01 |
| D2 232310 | | <0.005 | <0.05 | 0.02 | D2 232350 | | <0.005 | <0.05 | 0.04 |
| D2 232311 | | <0.005 | <0.05 | <0.01 | D2 232352 | | <0.005 | <0.05 | <0.01 |
| D2 232312 | | <0.005 | <0.05 | <0.01 | D2 232353 | | <0.005 | <0.05 | <0.01 |
| D2 232313 | | <0.005 | 0.08 | <0.01 | D2 232354 | | <0.005 | <0.05 | <0.01 |
| D2 232314 | | <0.005 | 0.12 | <0.01 | D2 232355 | | <0.005 | <0.05 | <0.01 |
| D2 232315 | | <0.005 | <0.05 | <0.01 | D2 232356 | | <0.005 | <0.05 | <0.01 |
| D2 232316 | | <0.005 | <0.05 | <0.01 | D2 232357 | | <0.005 | <0.05 | <0.01 |
| D2 232317 | | <0.005 | <0.05 | <0.01 | D2 232358 | | <0.005 | <0.05 | <0.01 |
| D2 232318 | | <0.005 | <0.05 | <0.01 | D2 232359 | | <0.005 | 0.10 | <0.01 |
| D2 232319 | | <0.005 | 0.13 | <0.01 | D2 232360 | | <0.005 | <0.05 | <0.01 |
| D2 232320 | | <0.005 | 0.15 | <0.01 | D2 232421 | | <0.005 | <0.05 | <0.01 |
| D2 232321 | | <0.005 | <0.05 | <0.01 | D2 232422 | | <0.005 | <0.05 | <0.01 |
| D2 232322 | | <0.005 | 0.06 | <0.01 | | | | | |
| D2 232323 | | <0.005 | <0.05 | <0.01 | | | | | |
| D2 232324 | | <0.005 | <0.05 | <0.01 | | | | | |
| D2 232325 | | <0.005 | <0.05 | <0.01 | | | | | |
| D2 232326 | | <0.005 | <0.05 | <0.01 | | | | | |
| D2 232327 | | <0.005 | <0.05 | <0.01 | | | | | |
| D2 232328 | | <0.005 | <0.05 | <0.01 | | | | | |
| D2 232329 | | <0.005 | <0.05 | <0.01 | | | | | |
| D2 232330 | | <0.005 | <0.05 | <0.01 | | | | | |
| D2 232331 | | <0.005 | <0.05 | <0.01 | | | | | |
| D2 232332 | | <0.005 | 0.13 | <0.01 | | | | | |
| D2 232333 | | <0.005 | <0.05 | <0.01 | | | | | |
| D2 232334 | | <0.005 | <0.05 | <0.01 | | | | | |
| D2 232335 | | 0.006 | <0.05 | <0.01 | | | | | |
| D2 232336 | | <0.005 | <0.05 | <0.01 | | | | | |
| D2 232337 | | 0.094 | <0.05 | 0.07 | | | | | |
| D2 232338 | | <0.005 | <0.05 | <0.01 | | | | | |
| D2 232339 | | <0.005 | <0.05 | <0.01 | | | | | |
| D2 232340 | | <0.005 | <0.05 | <0.01 | | | | | |



BONDAR CLEGG

MINT: BEAU PRE EXPLORATIONS LTD.

MORT: V01-00288.0 (COMPLETE)

PROJECT: VF-2000

DATE RECEIVED: 19-FEB-01

DATE PRINTED: 24-FEB-01

PAGE 1A (1 / 4)

| SAMPLE
NUMBER | ELEMENT
UNITS | WT (-)
g | WT (+)
g | Au (-)
OPT | Au (+)
OPT | Au Tot
OPT | Ag-150
OPT | Ag+150
OPT | Ag Tot
OPT | Ag
PPM | Cu
PPM | Pb
PPM | Mn
PPM |
|------------------|------------------|-------------|-------------|---------------|---------------|---------------|---------------|---------------|---------------|-----------|-----------|-----------|-----------|
| 232401 | | 131.9 | 4.86 | <0.005 | <0.01 | <0.005 | <0.05 | <0.05 | <0.05 | <0.2 | 34 | <2 | 52 |
| 232402 | | 304.9 | 6.55 | <0.005 | <0.01 | <0.005 | <0.05 | <0.05 | <0.05 | <0.2 | 28 | <2 | 51 |
| 232403 | | 214.4 | 9.39 | <0.005 | <0.01 | <0.005 | <0.05 | <0.05 | <0.05 | <0.2 | 53 | <2 | 97 |
| 232404 | | 228.5 | 2.17 | 0.016 | 0.32 | 0.019 | <0.05 | <0.05 | <0.05 | <0.2 | 14 | <2 | 47 |
| 232405 | | 251.3 | 8.71 | <0.005 | <0.01 | <0.005 | <0.05 | <0.05 | <0.05 | 0.4 | 54 | <2 | 103 |
| 232406 | | 218.1 | 4.22 | <0.005 | <0.01 | <0.005 | <0.05 | <0.05 | <0.05 | <0.2 | 50 | <2 | 76 |
| 232407 | | 222.7 | 3.50 | <0.005 | <0.01 | <0.005 | <0.05 | <0.05 | <0.05 | <0.2 | 18 | <2 | 61 |
| 232408 | | 265.0 | 3.70 | <0.005 | <0.01 | <0.005 | <0.05 | <0.05 | <0.05 | <0.2 | 31 | <2 | 77 |
| 232409 | | 166.8 | 2.09 | <0.005 | <0.01 | <0.005 | <0.05 | <0.05 | <0.05 | <0.2 | 29 | <2 | 74 |
| 232410 | | 262.4 | 2.82 | <0.005 | <0.01 | <0.005 | <0.05 | <0.05 | <0.05 | <0.2 | 19 | <2 | 68 |
| 232411 | | 271.5 | 7.00 | <0.005 | <0.01 | <0.005 | <0.05 | <0.05 | <0.05 | <0.2 | 20 | <2 | 72 |
| 232412 | | 219.6 | 1.54 | <0.005 | <0.01 | <0.005 | <0.05 | <0.05 | <0.05 | <0.2 | 19 | <2 | 73 |
| 232413 | | 201.4 | 3.65 | <0.005 | <0.01 | <0.005 | <0.05 | <0.05 | <0.05 | <0.2 | 11 | <2 | 62 |
| 232414 | | 232.6 | 2.12 | <0.005 | <0.01 | <0.005 | <0.05 | <0.05 | <0.05 | <0.2 | 20 | <2 | 69 |
| 232415 | | 221.0 | 4.16 | <0.005 | <0.01 | <0.005 | <0.05 | <0.05 | <0.05 | <0.2 | 21 | <2 | 66 |
| 232416 | | 226.1 | 1.82 | <0.005 | <0.01 | <0.005 | <0.05 | <0.05 | <0.05 | <0.2 | 25 | <2 | 67 |
| 232417 | | 189.4 | 1.53 | <0.005 | <0.01 | <0.005 | <0.05 | <0.05 | <0.05 | <0.2 | 44 | <2 | 81 |
| 232418 | | 178.9 | 0.25 | <0.005 | <0.01 | <0.005 | <0.05 | <0.05 | <0.05 | <0.2 | 17 | <2 | 60 |
| 232419 | | 233.6 | 1.64 | <0.005 | <0.01 | <0.005 | <0.05 | <0.05 | <0.05 | <0.2 | 14 | <2 | 68 |
| 232420 | | 286.7 | 2.28 | <0.005 | <0.01 | <0.005 | <0.05 | <0.05 | <0.05 | <0.2 | 26 | <2 | 75 |



BONDAR CLEGG

CLIENT: BEAU PRE EXPLORATIONS LTD.
 REPORT: V01-00288.0 (COMPLETE)

PROJECT: VF-2000

DATE RECEIVED: 19-FEB-01

DATE PRINTED: 24-FEB-01

PAGE 1B (2 / 4)

| SAMPLE NUMBER | ELEMENT UNITS | Mo PPM | Ni PPM | Co PPM | Cd PPM | Bi PPM | As PPM | Sb PPM | Fe PCT | Mn PPM | Tl PPM | Ba PPM | Cr PPM |
|---------------|---------------|--------|--------|--------|--------|--------|--------|--------|--------|--------|--------|--------|--------|
| DW 232401 | 2 | 35 | 15 | <0.2 | <5 | 7 | <5 | 3.67 | 328 | <10 | 324 | 154 | |
| DW 232402 | 2 | 27 | 13 | <0.2 | <5 | <5 | <5 | 3.29 | 314 | <10 | 221 | 114 | |
| DW 232403 | <1 | 45 | 18 | <0.2 | <5 | 271 | <5 | 4.35 | 336 | <10 | 285 | 113 | |
| DW 232404 | 5 | 18 | 8 | <0.2 | <5 | 694 | <5 | 2.26 | 244 | <10 | 218 | 202 | |
| DW 232405 | 1 | 46 | 18 | 0.2 | <5 | 9 | <5 | 4.67 | 411 | <10 | 272 | 104 | |
| DW 232406 | 2 | 47 | 18 | <0.2 | <5 | 7 | <5 | 4.55 | 455 | <10 | 247 | 122 | |
| DW 232407 | 2 | 25 | 12 | <0.2 | <5 | <5 | <5 | 2.91 | 300 | <10 | 255 | 133 | |
| DW 232408 | 2 | 28 | 15 | <0.2 | <5 | <5 | <5 | 3.32 | 470 | <10 | 475 | 101 | |
| DW 232409 | 1 | 28 | 14 | <0.2 | <5 | <5 | <5 | 3.29 | 471 | <10 | 421 | 132 | |
| DW 232410 | 2 | 23 | 13 | <0.2 | <5 | <5 | <5 | 3.10 | 404 | <10 | 366 | 98 | |
| DW 232411 | 2 | 25 | 14 | <0.2 | <5 | <5 | <5 | 3.23 | 433 | <10 | 393 | 103 | |
| DW 232412 | 2 | 25 | 15 | <0.2 | <5 | 32 | <5 | 3.37 | 432 | <10 | 456 | 123 | |
| DW 232413 | 2 | 24 | 12 | <0.2 | <5 | 29 | <5 | 2.64 | 421 | <10 | 276 | 143 | |
| DW 232414 | 3 | 23 | 13 | <0.2 | <5 | 40 | <5 | 3.28 | 431 | <10 | 352 | 137 | |
| DW 232415 | 2 | 25 | 14 | <0.2 | <5 | 17 | <5 | 3.26 | 395 | <10 | 501 | 139 | |
| DW 232416 | 3 | 25 | 15 | <0.2 | <5 | 19 | <5 | 3.35 | 448 | <10 | 435 | 137 | |
| DW 232417 | 2 | 35 | 18 | 0.2 | 6 | 5 | <5 | 4.29 | 587 | <10 | 111 | 129 | |
| DW 232418 | 5 | 20 | 10 | <0.2 | <5 | 5 | <5 | 2.54 | 342 | <10 | 278 | 182 | |
| DW 232419 | 2 | 23 | 12 | <0.2 | <5 | 6 | <5 | 2.97 | 400 | <10 | 240 | 136 | |
| DW 232420 | 2 | 26 | 14 | <0.2 | <5 | 9 | <5 | 3.39 | 425 | <10 | 345 | 121 | |



BONDAR CLEGG

CLIENT: BEAU PRE EXPLORATIONS LTD.
REPORT: V01-00288.0 (COMPLETE)

PROJECT: VF-2000

DATE RECEIVED: 19-FEB-01

DATE PRINTED: 24-FEB-01

PAGE 1C (3 / 4)

| SAMPLE NUMBER | ELEMENT UNITS | V PPM | Sn PPM | W PPM | La PPM | Al PCT | Mg PCT | Ca PCT | Na PCT | K PCT | Sr PPM | Y PPM | Ga PPM |
|---------------|---------------|-------|--------|-------|--------|--------|--------|--------|--------|-------|--------|-------|--------|
| DW 232401 | | 94 | <20 | <20 | 11 | 2.95 | 1.23 | 0.22 | 0.10 | 1.20 | 21 | 4 | 8 |
| DW 232402 | | 79 | <20 | <20 | 11 | 2.54 | 1.11 | 0.20 | 0.09 | 0.98 | 14 | 3 | 6 |
| DW 232403 | | 92 | <20 | <20 | 9 | 2.95 | 1.34 | 0.26 | 0.09 | 1.45 | 18 | 4 | 8 |
| DW 232404 | | 55 | <20 | 89 | 4 | 2.44 | 0.68 | 0.63 | 0.22 | 0.79 | 52 | 4 | 5 |
| DW 232405 | | 90 | <20 | <20 | 8 | 2.86 | 1.37 | 0.30 | 0.07 | 1.52 | 19 | 4 | 8 |
| DW 232406 | | 82 | <20 | <20 | 9 | 2.76 | 1.37 | 0.58 | 0.06 | 1.27 | 25 | 4 | 8 |
| DW 232407 | | 81 | <20 | <20 | 10 | 2.29 | 1.08 | 0.63 | 0.13 | 0.83 | 27 | 5 | 6 |
| DW 232408 | | 82 | <20 | <20 | 7 | 2.68 | 1.13 | 0.50 | 0.12 | 1.47 | 31 | 5 | 8 |
| DW 232409 | | 81 | <20 | <20 | 6 | 2.63 | 1.10 | 0.80 | 0.15 | 1.44 | 57 | 5 | 7 |
| DW 232410 | | 79 | <20 | <20 | 6 | 2.25 | 0.99 | 0.43 | 0.11 | 1.33 | 27 | 4 | 6 |
| DW 232411 | | 82 | <20 | <20 | 7 | 2.40 | 1.04 | 0.54 | 0.13 | 1.39 | 32 | 5 | 8 |
| DW 232412 | | 92 | <20 | <20 | 9 | 2.60 | 1.11 | 0.37 | 0.17 | 1.40 | 30 | 6 | 8 |
| DW 232413 | | 62 | <20 | <20 | 7 | 2.07 | 0.92 | 0.79 | 0.11 | 1.06 | 28 | 6 | 5 |
| DW 232414 | | 82 | <20 | <20 | 8 | 2.77 | 1.08 | 1.05 | 0.14 | 1.22 | 75 | 7 | 7 |
| DW 232415 | | 93 | <20 | <20 | 5 | 2.81 | 1.10 | 1.02 | 0.22 | 1.28 | 76 | 5 | 7 |
| DW 232416 | | 87 | <20 | <20 | 5 | 2.53 | 1.13 | 0.92 | 0.16 | 1.39 | 49 | 5 | 7 |
| DW 232417 | | 127 | <20 | <20 | 4 | 2.49 | 1.34 | 1.71 | 0.13 | 1.48 | 36 | 6 | 11 |
| DW 232418 | | 66 | <20 | <20 | 6 | 2.21 | 0.86 | 0.89 | 0.16 | 0.83 | 68 | 5 | 6 |
| DW 232419 | | 71 | <20 | <20 | 7 | 2.16 | 0.94 | 0.30 | 0.09 | 1.11 | 28 | 6 | 6 |
| DW 232420 | | 84 | <20 | <20 | 7 | 2.85 | 1.16 | 0.86 | 0.17 | 1.29 | 63 | 5 | 7 |



BONDAR CLEGG

CLIENT: BEAU PRE EXPLORATIONS LTD.
REPORT: V01-00288.0 (COMPLETE)

PROJECT: VF-2000

DATE RECEIVED: 19-FEB-01

DATE PRINTED: 24-FEB-01

PAGE 1D (1 / 4)

| SAMPLE NUMBER | ELEMENT UNITS | L1 | Nb
PPM | Sc
PPM | Ta
PPM | Tl
PCT | Zr
PPM | S
PCT |
|---------------|---------------|----|-----------|-----------|-----------|-----------|-----------|----------|
| DW 232401 | | 39 | 5 | 8 | <10 | 0.147 | 2 | 0.13 |
| DW 232402 | | 33 | 5 | 6 | <10 | 0.129 | 2 | 0.21 |
| DW 232403 | | 44 | 6 | 7 | <10 | 0.159 | 2 | 0.50 |
| DW 232404 | | 23 | 4 | <5 | <10 | 0.092 | 2 | 0.17 |
| DW 232405 | | 42 | 6 | 7 | <10 | 0.167 | 2 | 0.53 |
| DW 232406 | | 39 | 5 | 6 | <10 | 0.132 | 2 | 0.37 |
| DW 232407 | | 28 | 4 | 6 | <10 | 0.111 | 2 | 0.12 |
| DW 232408 | | 31 | 5 | 7 | <10 | 0.214 | 2 | 0.25 |
| X 232409 | | 29 | 5 | 7 | <10 | 0.211 | 2 | 0.27 |
| DW 232410 | | 27 | 5 | 7 | <10 | 0.213 | 2 | 0.20 |
| X 232411 | | 28 | 4 | 7 | <10 | 0.227 | 2 | 0.23 |
| DW 232412 | | 30 | 5 | 9 | <10 | 0.217 | 2 | 0.18 |
| DW 232413 | | 26 | 3 | <5 | <10 | 0.164 | 2 | 0.10 |
| DW 232414 | | 31 | 5 | 7 | <10 | 0.190 | 2 | 0.19 |
| DW 232415 | | 29 | 5 | 7 | <10 | 0.216 | 2 | 0.24 |
| DW 232416 | | 27 | 5 | 8 | <10 | 0.220 | 2 | 0.29 |
| DW 232417 | | 27 | 6 | 8 | <10 | 0.249 | 2 | 0.97 |
| DW 232418 | | 27 | 4 | 5 | <10 | 0.149 | 2 | 0.33 |
| DW 232419 | | 30 | 4 | 5 | <10 | 0.196 | 2 | 0.24 |
| DW 232420 | | 37 | 5 | 6 | <10 | 0.170 | 2 | 0.21 |



BONDAR CLEGG



Geochemical
Lab
Report

PK

BEAU PRE EXPLORATIONS LTD.
110 - 850 BLANSHARD ST
VICTORIA, BC V8W 2H2

+

+

+

+



BONDAR CLEGG



Geochemical Lab Report

REPORT: V01-00288.0 (COMPLETE)

REFERENCE:

CLIENT: BEAU PRE EXPLORATIONS LTD.

SUBMITTED BY: UNKNOWN

PROJECT: VF-2000

DATE RECEIVED: 19-FEB-01 DATE PRINTED: 28-FEB-01

| DATE APPROVED | ELEMENT | NUMBER OF ANALYSES | LOWER DETECTION | EXTRACTION | METHOD | DATE APPROVED | ELEMENT | NUMBER OF ANALYSES | LOWER DETECTION | EXTRACTION | METHOD |
|---|--------------------------------|--------------------|-----------------|----------------|---------------------|---------------|---------|--------------------|-----------------|------------|----------------|
| 010221 | 1 Wt (-) Pulp Wt. Minus Fract. | 20 | g | | FIRE ASSAY | 010221 | 37 Li | Li - IC01 | 20 | 1 PPM | HCL:HNO3 (3:1) |
| 010221 | 2 WT (+) Pulp wt. Plus Fract | 20 | 0.01 g | | FIRE ASSAY | 010221 | 38 Nb | Nb - IC01 | 20 | 1 PPM | HCL:HNO3 (3:1) |
| 010221 | 3 Au (-) Gold. Minus Fraction | 20 | 0.001 OPT | | FIRE ASSAY | 010221 | 39 Sc | Sc - IC01 | 20 | 5 PPM | HCL:HNO3 (3:1) |
| 010221 | 4 Au (+) Gold. Plus Fraction | 20 | 0.01 OPT | | FIRE ASSAY | 010221 | 40 Ta | Ta - IC01 | 20 | 10 PPM | HCL:HNO3 (3:1) |
| 010221 | 5 Au Tot Gold in total sample | 20 | 0.005 OPT | | FIRE ASSAY | 010221 | 41 Ti | Ti - IC01 | 20 | 0.010 PCT | HCL:HNO3 (3:1) |
| 010221 | 6 Ag-150 Silver Avg-150 mesh. | 20 | 0.02 OPT | | FIRE ASSAY | 010221 | 42 Zr | Zr - IC01 | 20 | 1 PPM | HCL:HNO3 (3:1) |
| 010221 | 7 Ag+150 Silver in +150 mesh. | 20 | 0.05 OPT | | FIRE ASSAY | 010221 | 43 S | S - IC01 | 20 | 0.01 PCT | HCL:HNO3 (3:1) |
| 010221 | 8 Ag Tot Ag in total sample. | 20 | 0.05 OPT | | FIRE ASSAY | | | | | | |
| 010221 | 9 Ag Ag - IC01 | 20 | 0.2 PPM | HCL:HNO3 (3:1) | INDUC. COUP. PLASMA | | | | | | |
| 010221 | 10 Cu Cu - IC01 | 20 | 1 PPM | HCL:HNO3 (3:1) | INDUC. COUP. PLASMA | | | | | | |
| 010221 | 11 Pb Pb - IC01 | 20 | 2 PPM | HCL:HNO3 (3:1) | INDUC. COUP. PLASMA | | | | | | |
| 010221 | 12 Zn Zn - IC01 | 20 | 1 PPM | HCL:HNO3 (3:1) | INDUC. COUP. PLASMA | | | | | | |
| 010221 | 13 Mo Mo - IC01 | 20 | 1 PPM | HCL:HNO3 (3:1) | INDUC. COUP. PLASMA | | | | | | |
| 010221 | 14 Ni Ni - IC01 | 20 | 1 PPM | HCL:HNO3 (3:1) | INDUC. COUP. PLASMA | | | | | | |
| 010221 | 15 Co Co - IC01 | 20 | 1 PPM | HCL:HNO3 (3:1) | INDUC. COUP. PLASMA | | | | | | |
| 010221 | 16 Cd Cd - IC01 | 20 | 0.2 PPM | HCL:HNO3 (3:1) | INDUC. COUP. PLASMA | | | | | | |
| 010221 | 17 Bi Bi - IC01 | 20 | 5 PPM | HCL:HNO3 (3:1) | INDUC. COUP. PLASMA | | | | | | |
| 010221 | 18 As As - IC01 | 20 | 5 PPM | HCL:HNO3 (3:1) | INDUC. COUP. PLASMA | | | | | | |
| 010221 | 19 Sb Sb - IC01 | 20 | 5 PPM | HCL:HNO3 (3:1) | INDUC. COUP. PLASMA | | | | | | |
| 010221 | 20 Fe Fe - IC01 | 20 | 0.01 PCT | HCL:HNO3 (3:1) | INDUC. COUP. PLASMA | | | | | | |
| 010221 | 21 Mn Mn - IC01 | 20 | 1 PPM | HCL:HNO3 (3:1) | INDUC. COUP. PLASMA | | | | | | |
| 010221 | 22 Te Te - IC01 | 20 | 10 PPM | HCL:HNO3 (3:1) | INDUC. COUP. PLASMA | | | | | | |
| 010221 | 23 Ba Ba - IC01 | 20 | 1 PPM | HCL:HNO3 (3:1) | INDUC. COUP. PLASMA | | | | | | |
| 010221 | 24 Cr Cr - IC01 | 20 | 1 PPM | HCL:HNO3 (3:1) | INDUC. COUP. PLASMA | | | | | | |
| 010221 | 25 V V - IC01 | 20 | 1 PPM | HCL:HNO3 (3:1) | INDUC. COUP. PLASMA | | | | | | |
| 010221 | 26 Sn Sn - IC01 | 20 | 20 PPM | HCL:HNO3 (3:1) | INDUC. COUP. PLASMA | | | | | | |
| 010221 | 27 W W - IC01 | 20 | 20 PPM | HCL:HNO3 (3:1) | INDUC. COUP. PLASMA | | | | | | |
| 010221 | 28 La La - IC01 | 20 | 1 PPM | HCL:HNO3 (3:1) | INDUC. COUP. PLASMA | | | | | | |
| 010221 | 29 Al Al - IC01 | 20 | 0.01 PCT | HCL:HNO3 (3:1) | INDUC. COUP. PLASMA | | | | | | |
| 010221 | 30 Mg Mg - IC01 | 20 | 0.01 PCT | HCL:HNO3 (3:1) | INDUC. COUP. PLASMA | | | | | | |
| 010221 | 31 Ca Ca - IC01 | 20 | 0.01 PCT | HCL:HNO3 (3:1) | INDUC. COUP. PLASMA | | | | | | |
| 010221 | 32 Na Na - IC01 | 20 | 0.01 PCT | HCL:HNO3 (3:1) | INDUC. COUP. PLASMA | | | | | | |
| 010221 | 33 K K - IC01 | 20 | 0.01 PCT | HCL:HNO3 (3:1) | INDUC. COUP. PLASMA | | | | | | |
| 010221 | 34 Sr Sr - IC01 | 20 | 1 PPM | HCL:HNO3 (3:1) | INDUC. COUP. PLASMA | | | | | | |
| 010221 | 35 Y Y - IC01 | 20 | 1 PPM | HCL:HNO3 (3:1) | INDUC. COUP. PLASMA | | | | | | |
| 010221 | 36 Ga Ga - IC01 | 20 | 2 PPM | HCL:HNO3 (3:1) | INDUC. COUP. PLASMA | | | | | | |
| SAMPLE TYPES | | | | | | | | | | | |
| NUMBER | | | | | | | | | | | |
| SIZE FRACTIONS | | | | | | | | | | | |
| NUMBER | | | | | | | | | | | |
| SAMPLE PREPARATIONS | | | | | | | | | | | |
| NUMBER | | | | | | | | | | | |
| D DRILL CORE | | | | | | | | | | | |
| 20 | | | | | | | | | | | |
| W +150/-150 | | | | | | | | | | | |
| 20 | | | | | | | | | | | |
| CRUSH/SPLIT & PULV. | | | | | | | | | | | |
| OVERWEIGHT/KG | | | | | | | | | | | |
| 5 | | | | | | | | | | | |
| METALLICS SCREENING | | | | | | | | | | | |
| 20 | | | | | | | | | | | |
| REPORT COPIES TO: 110 - 850 BLANSHARD ST | | | | | | | | | | | |
| INVOICE TO: 110 - 850 BLANSHARD ST | | | | | | | | | | | |
| ***** | | | | | | | | | | | |
| This report must not be reproduced except in full. The data presented in this | | | | | | | | | | | |
| report is specific to those samples identified under "Sample Number" and is | | | | | | | | | | | |
| applicable only to the samples as received expressed on a dry basis unless | | | | | | | | | | | |
| otherwise indicated | | | | | | | | | | | |
| ***** | | | | | | | | | | | |





BONDAR CLEGG



Geochemical Lab Report

CLIENT: BEAU PRE EXPLORATIONS LTD.
REPORT: V01-00288.0 (COMPLETE)

PROJECT: VF-2009

DATE RECEIVED: 19-FEB-01

DATE PRINTED: 28-FEB-0

PAGE 1AC 1 / 6

| SAMPLE NUMBER | ELEMENT | | WT (-) | WT (+) | AU (-) | AU (+) | AU Tot | Ag-150 | Ag+150 | Ag Tot | Ag | Cu | Pb | Zn | Mo | Ni | Co | Cd | Bi | As | Sb | Fe | Mn | TE | Ba | Cr | V | Sn | W | La | Al | Mg | Ca | Na | K | Sr | Y |
|---------------|---------|--|--------|--------|--------|--------|--------|--------|--------|--------|-----|-----|-----|-----|-----|-----|-----|-----|-----|-----|-----|------|-----|-----|-----|-----|------|-----|-----|-----|------|------|------|------|------|----|---|
| | UNITS | | g | g | OPT | OPT | OPT | OPT | OPT | OPT | PPM | PCT | PPM | PPM | PPM | PPM | PPM | PPM | PCT | PCT | PCT | PCT | PPM | PPM | | | | |
| 232401 | | | 131.9 | 4.86 | <0.005 | <0.01 | <0.005 | <0.05 | <0.05 | <0.05 | <2 | 34 | <2 | 52 | 2 | 35 | 15 | <2 | <5 | 7 | <5 | 3.67 | 328 | <10 | 324 | 154 | .94 | <20 | <20 | 11 | 2.95 | 1.23 | 0.22 | 0.10 | 1.20 | 21 | 4 |
| 232402 | | | 304.9 | 6.55 | <0.005 | <0.01 | <0.005 | <0.05 | <0.05 | <0.05 | <2 | 28 | <2 | 51 | 2 | 27 | 13 | <2 | <5 | <5 | <5 | 3.29 | 314 | <10 | 221 | 114 | .79 | <20 | <20 | 11 | 2.54 | 1.11 | 0.20 | 0.09 | 0.98 | 14 | 3 |
| 232403 | | | 214.5 | 9.39 | <0.005 | <0.01 | <0.005 | <0.05 | <0.05 | <0.05 | <2 | 53 | <2 | 97 | <1 | 45 | 18 | <2 | <5 | 271 | <5 | 4.35 | 336 | <10 | 285 | 113 | .92 | <20 | <20 | 9 | 2.95 | 1.34 | 0.26 | 0.09 | 1.45 | 18 | 4 |
| 232404 | | | 228.5 | 2.17 | 0.016 | 0.32 | 0.019 | <0.05 | <0.05 | <0.05 | <2 | 14 | <2 | 47 | 5 | 18 | 8 | <2 | <5 | 694 | <5 | 2.26 | 244 | <10 | 218 | 202 | .55 | <20 | .89 | 4 | 2.44 | 0.68 | 0.63 | 0.22 | 0.79 | 52 | 4 |
| 232405 | | | 251.3 | 8.71 | <0.005 | <0.01 | <0.005 | <0.05 | <0.05 | <0.05 | 0.4 | 54 | <2 | 103 | 1 | 46 | 18 | 0.2 | <5 | 9 | <5 | 4.67 | 411 | <10 | 272 | 104 | .90 | <20 | <20 | 8 | 2.86 | 1.37 | 0.39 | 0.07 | 1.52 | 19 | 4 |
| 232406 | | | 218.1 | 4.22 | <0.005 | <0.01 | <0.005 | <0.05 | <0.05 | <0.05 | <2 | 50 | <2 | 76 | 2 | 47 | 18 | <2 | <5 | 7 | <5 | 4.55 | 455 | <10 | 247 | 122 | .82 | <20 | <20 | 9 | 2.76 | 1.37 | 0.58 | 0.06 | 1.27 | 25 | 4 |
| 232407 | | | 222.7 | 3.50 | <0.005 | <0.01 | <0.005 | <0.05 | <0.05 | <0.05 | <2 | 18 | <2 | 61 | 2 | 25 | 12 | <2 | <5 | <5 | <5 | 2.91 | 300 | <10 | 255 | 133 | .81 | <20 | <20 | 10 | 2.29 | 1.08 | 0.63 | 0.13 | 0.83 | 27 | 5 |
| 232408 | | | 265.0 | 3.70 | <0.005 | <0.01 | <0.005 | <0.05 | <0.05 | <0.05 | <2 | 31 | <2 | 77 | 2 | 28 | 15 | <2 | <5 | <5 | <5 | 3.32 | 470 | <10 | 475 | 101 | .82 | <20 | <20 | 7 | 2.68 | 1.13 | 0.50 | 0.12 | 1.47 | 31 | 5 |
| 232409 | | | 166.8 | 2.09 | <0.005 | <0.01 | <0.005 | <0.05 | <0.05 | <0.05 | <2 | 29 | <2 | 74 | 1 | 28 | 14 | <2 | <5 | <5 | <5 | 3.29 | 471 | <10 | 421 | 132 | .81 | <20 | <20 | 6 | 2.63 | 1.10 | 0.80 | 0.15 | 1.44 | 57 | 5 |
| 232410 | | | 262.4 | 2.82 | <0.005 | <0.01 | <0.005 | <0.05 | <0.05 | <0.05 | <2 | 19 | <2 | 68 | 2 | 23 | 13 | <2 | <5 | <5 | <5 | 3.10 | 404 | <10 | 366 | 98 | .79 | <20 | <20 | 6 | 2.25 | 0.99 | 0.43 | 0.11 | 1.33 | 27 | 4 |
| 232411 | | | 271.5 | 7.00 | <0.005 | <0.01 | <0.005 | <0.05 | <0.05 | <0.05 | <2 | 20 | <2 | 72 | 2 | 25 | 14 | <2 | <5 | <5 | <5 | 3.23 | 433 | <10 | 393 | 103 | .82 | <20 | <20 | 7 | 2.40 | 1.04 | 0.54 | 0.13 | 1.39 | 32 | 5 |
| 232412 | | | 219.6 | 1.54 | <0.005 | <0.01 | <0.005 | <0.05 | <0.05 | <0.05 | <2 | 19 | <2 | 73 | 2 | 25 | 15 | <2 | <5 | 32 | <5 | 3.37 | 432 | <10 | 456 | 123 | .92 | <20 | <20 | 9 | 2.60 | 1.11 | 0.37 | 0.17 | 1.40 | 30 | 6 |
| 232413 | | | 201.4 | 3.65 | <0.005 | <0.01 | <0.005 | <0.05 | <0.05 | <0.05 | <2 | 11 | <2 | 62 | 2 | 24 | 12 | <2 | <5 | 29 | <5 | 2.64 | 421 | <10 | 276 | 143 | .62 | <20 | <20 | 7 | 2.07 | 0.92 | 0.79 | 0.11 | 1.06 | 28 | 6 |
| 232414 | | | 232.6 | 2.12 | <0.005 | <0.01 | <0.005 | <0.05 | <0.05 | <0.05 | <2 | 20 | <2 | 69 | 3 | 23 | 13 | <2 | <5 | 40 | <5 | 3.28 | 431 | <10 | 352 | 137 | .82 | <20 | <20 | 8 | 2.77 | 1.08 | 1.05 | 0.14 | 1.22 | 75 | 7 |
| 232415 | | | 221.0 | 4.16 | <0.005 | <0.01 | <0.005 | <0.05 | <0.05 | <0.05 | <2 | 21 | <2 | 66 | 2 | 25 | 14 | <2 | <5 | 17 | <5 | 3.26 | 395 | <10 | 501 | 139 | .93 | <20 | <20 | 5 | 2.81 | 1.10 | 1.02 | 0.22 | 1.28 | 76 | 5 |
| 232416 | | | 226.1 | 1.82 | <0.005 | <0.01 | <0.005 | <0.05 | <0.05 | <0.05 | <2 | 25 | <2 | 67 | 3 | 25 | 15 | <2 | <5 | 19 | <5 | 3.35 | 448 | <10 | 435 | 137 | .87 | <20 | <20 | 5 | 2.53 | 1.13 | 0.92 | 0.16 | 1.39 | 49 | 5 |
| 232417 | | | 189.5 | 1.53 | <0.005 | <0.01 | <0.005 | <0.05 | <0.05 | <0.05 | <2 | 44 | <2 | 81 | 2 | 35 | 18 | 0.2 | 6 | 5 | <5 | 4.29 | 587 | <10 | 111 | 129 | .127 | <20 | <20 | 4 | 2.49 | 1.34 | 1.71 | 0.13 | 1.48 | 36 | 6 |
| 232418 | | | 178.9 | 0.25 | <0.005 | <0.01 | <0.005 | <0.05 | <0.05 | <0.05 | <2 | 17 | <2 | 60 | 5 | 20 | 10 | <2 | <5 | 5 | <5 | 2.54 | 342 | <10 | 278 | 182 | .66 | <20 | <20 | 6 | 2.21 | 0.86 | 0.89 | 0.16 | 0.83 | 68 | 5 |
| 232419 | | | 233.6 | 1.64 | <0.005 | <0.01 | <0.005 | <0.05 | <0.05 | <0.05 | <2 | 14 | <2 | 68 | 2 | 23 | 12 | <2 | <5 | 6 | <5 | 2.97 | 400 | <10 | 240 | 136 | .71 | <20 | <20 | 7 | 2.16 | 0.94 | 0.30 | 0.09 | 1.11 | 28 | 6 |
| 232420 | | | 286.7 | 2.28 | <0.005 | <0.01 | <0.005 | <0.05 | <0.05 | <0.05 | <2 | 26 | <2 | 73 | 2 | 26 | 14 | <2 | <5 | 9 | <5 | 3.39 | 425 | <10 | 345 | 121 | .84 | <20 | <20 | 7 | 2.85 | 1.16 | 0.86 | 0.17 | 1.29 | 63 | 5 |



BONDAR CLEGG

Geochemical
Lab
ReportCLIENT: BEAU PRE EXPLORATIONS LTD.
REPORT: V01-00288.0 (COMPLETE)

PROJECT: VF-2000

DATE RECEIVED: 19-FEB-01

DATE PRINTED: 28-FEB-01

PAGE 1B(2 / 6)

| SAMPLE
NUMBER | ELEMENT
UNITS | Ga | Li | Nb | Sc | Ta | Ti | Zr | S |
|------------------|------------------|-----|-----|-----|-----|-----|-------|-----|------|
| | PPM | PPM | PPM | PPM | PPM | PPM | PCT | PPM | PCT |
| 232401 | | 8 | 39 | 5 | 8 | <10 | 0.147 | 2 | 0.13 |
| 232402 | | 6 | 33 | 5 | 6 | <10 | 0.129 | 2 | 0.21 |
| 232403 | | 8 | 44 | 6 | 7 | <10 | 0.159 | 2 | 0.50 |
| 232404 | | 5 | 23 | 4 | <5 | <10 | 0.092 | 2 | 0.17 |
| 232405 | | 8 | 42 | 6 | 7 | <10 | 0.167 | 2 | 0.53 |
| 232406 | | 8 | 39 | 5 | 6 | <10 | 0.132 | 2 | 0.37 |
| 232407 | | 6 | 28 | 4 | 6 | <10 | 0.111 | 2 | 0.12 |
| 232408 | | 8 | 31 | 5 | 7 | <10 | 0.214 | 2 | 0.25 |
| 232409 | | 7 | 29 | 5 | 7 | <10 | 0.211 | 2 | 0.27 |
| 232410 | | 6 | 27 | 5 | 7 | <10 | 0.213 | 2 | 0.20 |
| 232411 | | 8 | 28 | 4 | 7 | <10 | 0.227 | 2 | 0.23 |
| 232412 | | 8 | 30 | 5 | 9 | <10 | 0.217 | 2 | 0.18 |
| 232413 | | 5 | 26 | 3 | <5 | <10 | 0.164 | 2 | 0.10 |
| 232414 | | 7 | 31 | 5 | 7 | <10 | 0.190 | 2 | 0.19 |
| 232415 | | 7 | 29 | 5 | 7 | <10 | 0.216 | 2 | 0.24 |
| 232416 | | 7 | 27 | 5 | 8 | <10 | 0.220 | 2 | 0.29 |
| 232417 | | 11 | 27 | 6 | 8 | <10 | 0.249 | 2 | 0.97 |
| 232418 | | 6 | 27 | 4 | 5 | <10 | 0.149 | 2 | 0.33 |
| 232419 | | 6 | 30 | 4 | 5 | <10 | 0.196 | 2 | 0.24 |
| 232420 | | 7 | 37 | 5 | 6 | <10 | 0.170 | 2 | 0.21 |



BONDAR CLEGG



Geochemical Lab Report

CLIENT: BEAU PRE EXPLORATIONS LTD.

REPORT: V01-00288.0 (COMPLETE)

PROJECT: VF-2000

DATE RECEIVED: 19-FEB-01

DATE PRINTED: 28-FEB-01

PAGE 2A(3/ 6)

| STANDARD
NAME | ELEMENT
UNITS | Wt (-)
g | WT (+)
g | Au (-)
OPT | Au (+)
OPT | Au Tot
OPT | Ag-150
OPT | Ag+150
OPT | Ag Tot
OPT | Cu
PPM | Pb
PPM | Zn
PPM | Mo
PPM | Ni
PPM | Co
PPM | Cd
PPM | Bi
PPM | As
PPM | Sb
PPM | Fe
PPM | Mn
PPM | TE
PPM | Ba
PPM | Cr
PPM | V
PPM | Sn
PPM | W
PPM | La
PPM | Al
PPM | Mg
PPM | Ca
PPM | Na
PPM | K
PPM | Sr
PPM | Y
PPM | |
|--------------------|------------------|-------------|-------------|---------------|---------------|---------------|---------------|---------------|---------------|-----------|-----------|-----------|-----------|-----------|-----------|-----------|-----------|-----------|-----------|-----------|-----------|-----------|-----------|-----------|----------|-----------|----------|-----------|-----------|-----------|-----------|-----------|----------|-----------|----------|----|
| ANALYTICAL BLANK | - | - | <0.005 | - | - | <0.05 | - | - | <.2 | <1 | <2 | <1 | <1 | <1 | <.2 | <5 | <5 | <5 | <.01 | <1 | <10 | <1 | <1 | <1 | <20 | <20 | <1 | <.01 | <.01 | <.01 | <.01 | <1 | <1 | | | |
| Number of Analyses | - | - | 1 | - | - | 1 | - | - | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | | | | | |
| Mean Value | - | - | 0.002 | - | - | 0.02 | - | - | 0.1 | <1 | 1 | <1 | <1 | <1 | <1 | 0.1 | 3 | 3 | <.01 | <1 | 5 | <1 | <1 | <1 | 10 | 10 | <1 | <.01 | <.01 | <.01 | <.01 | <1 | <1 | | | |
| Standard Deviation | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | | | | | | |
| Accepted Value | <0.1 | <0.01 | <0.001 | <0.01 | <0.001 | <0.01 | <0.01 | <0.01 | 0.2 | 1 | 2 | 1 | 1 | 1 | 1 | 0.1 | 2 | 5 | 5 | 0.05 | 1 | <1 | <1 | 1 | 1 | <1 | <1 | <.01 | <.01 | <.01 | <.01 | <1 | <1 | | | |
| OX12 Oxide | - | 31.71 | - | 0.19 | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | | | | | |
| Number of Analyses | - | - | 1 | - | - | 1 | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | | | | | |
| Mean Value | - | 31.71 | - | 0.19 | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | | | | | |
| Standard Deviation | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | | | | | |
| Accepted Value | - | 0.192 | - | 0.30 | 0.30 | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | | | | | |
| CANMET LKSD-2 | - | - | - | - | - | - | - | - | - | 0.7 | 33 | 36 | 195 | <1 | 24 | 14 | 0.8 | <5 | 8 | <5 | 3.43 | 1546 | <10 | 201 | 28 | 40 | <20 | <20 | 55 | 1.65 | 0.59 | 0.58 | 0.03 | 0.21 | 22 | 26 |
| Number of Analyses | - | - | - | - | - | - | - | - | - | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | | | | |
| Mean Value | - | - | - | - | - | - | - | - | - | 0.7 | 33 | 36 | 195 | <1 | 24 | 14 | 0.8 | 3 | 8 | 3 | 3.43 | 1546 | 5 | 201 | 28 | 40 | 10 | 10 | 55 | 1.65 | 0.59 | 0.58 | 0.03 | 0.21 | 22 | 26 |
| Standard Deviation | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | | | | | |
| Accepted Value | - | - | - | - | - | - | - | - | - | 0.8 | 36 | 40 | 200 | 2 | 23 | 17 | 0.8 | - | 9 | 1 | 3.50 | 1840 | - | 211 | 29 | 48 | - | - | 58 | 1.68 | 0.60 | 0.58 | 0.04 | 0.26 | 30 | 29 |
| OX11 Oxide | - | 0.087 | - | 0.73 | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | | | | |
| Number of Analyses | - | - | 1 | - | - | 1 | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | | | | | |
| Mean Value | - | 0.087 | - | 0.73 | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | | | | | |
| Standard Deviation | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | | | | | |
| Accepted Value | - | 0.086 | - | 0.73 | 0.73 | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | - | | | | | |



BONPAR CLEGG



Geochemical Lab Report

CLIENT: BEAU PRE EXPLORATIONS LTD.
REPORT: V01-00288.0 (COMPLETE)

PROJECT: VF-2000

DATE RECEIVED: 19-FEB-01

DATE PRINTED: 28-FEB-01

PAGE 2B(4/ 6)

| STANDARD
NAME | ELEMENT
UNITS | Ga
PPM | Li
PPM | Nb
PPM | Sc
PPM | Ta
PPM | Ti
PPM | Zr
PCT | S
PPM |
|------------------|------------------|-----------|-----------|-----------|-----------|-----------|-----------|-----------|----------|
|------------------|------------------|-----------|-----------|-----------|-----------|-----------|-----------|-----------|----------|

| | | | | | | | | |
|--------------------|----|----|----|----|-----|-------|----|----|
| ANALYTICAL BLANK | <2 | <1 | <1 | <5 | <10 | <.010 | <1 | <1 |
| Number of Analyses | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 |
| Mean Value | 1 | <1 | <1 | 3 | 5 | 0.005 | <1 | <1 |
| Standard Deviation | - | - | - | - | - | - | - | - |
| Accepted Value | <1 | <1 | <1 | <1 | <1 | <.001 | <1 | <1 |

| | | | | | |
|--------------------|---|---|---|---|---|
| OX12 Oxide | - | - | - | - | - |
| Number of Analyses | - | - | - | - | - |
| Mean Value | - | - | - | - | - |
| Standard Deviation | - | - | - | - | - |
| Accepted Value | - | - | - | - | - |

| | | | | | | | | |
|--------------------|---|----|---|----|-----|-------|---|------|
| CANMET LKSD-2 | 6 | 18 | 5 | <5 | <10 | 0.064 | 5 | 0.16 |
| Number of Analyses | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 |
| Mean Value | 6 | 18 | 5 | 3 | 5 | 0.064 | 5 | 0.16 |
| Standard Deviation | - | - | - | - | - | - | - | - |
| Accepted Value | 4 | 18 | 6 | 7 | - | - | - | 0.16 |

| | | | | |
|--------------------|---|---|---|---|
| OX11 Oxide | - | - | - | - |
| Number of Analyses | - | - | - | - |
| Mean Value | - | - | - | - |
| Standard Deviation | - | - | - | - |
| Accepted Value | - | - | - | - |



BONDAR CLEGG



Geochemical Lab Report

CLIENT: BEAU PRE EXPLORATIONS LTD.

REPORT: V01-00288.0 (COMPLETE)

PROJECT: VF-2000

DATE RECEIVED: 19-FEB-01

DATE PRINTED: 28-FEB-0

PAGE 3AC 5/6



BONDAR CLEGG

Geochemical
Lab
Report

CLIENT: BEAU PRE EXPLORATIONS LTD.

REPORT: V01-00288.0 (COMPLETE)

PROJECT: VF-2000

DATE RECEIVED: 19-FEB-01

DATE PRINTED: 28-FEB-01

PAGE 3B(6/ 6)

| SAMPLE
NUMBER | ELEMENT | Ga | Li | Nb | Sc | Ta | Ti | Zr | S |
|------------------|---------|-----|-----|-----|-----|-----|-----|-----|-----|
| | UNITS | PPM | PPM | PPM | PPM | PPM | PCT | PPM | PCT |

| | | | | | | | | | |
|--------|---|----|---|---|-----|-------|---|------|--|
| 232406 | 8 | 39 | 5 | 6 | <10 | 0.132 | 2 | 0.37 | |
|--------|---|----|---|---|-----|-------|---|------|--|

Duplicate

| | | | | | | | | | |
|--------|---|----|---|---|-----|-------|---|------|--|
| 232409 | 7 | 29 | 5 | 7 | <10 | 0.211 | 2 | 0.27 | |
|--------|---|----|---|---|-----|-------|---|------|--|

Duplicate

| | | | | | | | | | |
|--------|---|----|---|---|-----|-------|---|------|--|
| 232418 | 6 | 27 | 4 | 5 | <10 | 0.149 | 2 | 0.33 | |
|--------|---|----|---|---|-----|-------|---|------|--|

Duplicate



BONDAR CLEGG



Geochemical Lab Report

REPORT: V01-00287.0 (COMPLETE)

REFERENCE:

CLIENT: BEAU PRE EXPLORATIONS LTD.

SUBMITTED BY: UNKNOWN

PROJECT: VF-2000

DATE RECEIVED: 19-FEB-01

DATE PRINTED: 26-FEB-01

| APPROVED | DATE | ORDER | ELEMENT | NUMBER OF ANALYSES | LOWER | | | METHOD |
|----------|--------|-------|-----------------------|--------------------|-------|-----------------|---|---------------------|
| | | | | | | DETECTION LIMIT | EXTRACTION | |
| | 010224 | 1 | AuGrav Gold (Grav.) | 61 | 0.005 | OPT | FIRE ASSAY | GRAVIMETRIC |
| | 010224 | 2 | AgGrav Silver (Grav.) | 61 | 0.05 | OPT | FIRE ASSAY | FIRE ASSAY-GRAV |
| | 010224 | 3 | As Arsenic | 61 | 0.01 | PCT | HF-HNO ₃ -HClO ₄ -HCl | AAS LOW LEVEL ASSAY |


| SAMPLE TYPES | NUMBER | SIZE FRACTIONS | NUMBER | SAMPLE PREPARATIONS | NUMBER |
|--------------|--------|----------------|--------|---------------------|--------|
| D DRILL CORE | 61 | 2 -150 | 61 | CRUSH/SPLIT & PULV. | 61 |

OVERWEIGHT/KG 102

REPORT COPIES TO: 110 - 850 BLANSHARD ST

INVOICE TO: 110 - 850 BLANSHARD ST

 This report must not be reproduced except in full. The data presented in this report is specific to those samples identified under "Sample Number" and is applicable only to the samples as received expressed on a dry basis unless otherwise indicated



BONDAR CLEGG



Geochemical Lab Report

CLIENT: BEAU PRE EXPLORATIONS LTD.

REPORT: V01-00287.0 (COMPLETE)

DATE RECEIVED: 19-FEB-01

PROJECT: VF-2000

DATE PRINTED: 26-FEB-01

PAGE 1 OF 3

| SAMPLE NUMBER | ELEMENT UNITS | AuGrav OPT | AgGrav OPT | As PCT | SAMPLE NUMBER | ELEMENT UNITS | AuGrav OPT | AgGrav OPT | As PCT |
|---------------|---------------|------------|------------|--------|---------------|---------------|------------|------------|--------|
| D2 232301 | | <0.005 | <0.05 | <0.01 | D2 232341 | | <0.005 | <0.05 | <0.01 |
| D2 232302 | | <0.005 | <0.05 | <0.01 | D2 232342 | | <0.005 | <0.05 | <0.01 |
| D2 232303 | | <0.005 | <0.05 | <0.01 | D2 232343 | | <0.005 | <0.05 | <0.01 |
| D2 232304 | | <0.005 | <0.05 | <0.01 | D2 232344 | | <0.005 | <0.05 | <0.01 |
| D2 232305 | | <0.005 | <0.05 | 0.04 | D2 232345 | | 0.116 | <0.05 | 0.34 |
| D2 232306 | | <0.005 | <0.05 | <0.01 | D2 232346 | | 0.005 | 0.13 | 0.08 |
| D2 232307 | | <0.005 | <0.05 | <0.01 | D2 232347 | | <0.005 | <0.05 | 0.04 |
| D2 232308 | | <0.005 | <0.05 | <0.01 | D2 232348 | | <0.005 | <0.05 | <0.01 |
| D2 232309 | | <0.005 | <0.05 | <0.01 | D2 232349 | | <0.005 | <0.05 | <0.01 |
| D2 232310 | | <0.005 | <0.05 | 0.02 | D2 232350 | | <0.005 | <0.05 | 0.04 |
| D2 232311 | | <0.005 | <0.05 | <0.01 | D2 232352 | | <0.005 | <0.05 | <0.01 |
| D2 232312 | | <0.005 | <0.05 | <0.01 | D2 232353 | | <0.005 | <0.05 | <0.01 |
| D2 232313 | | <0.005 | 0.08 | <0.01 | D2 232354 | | <0.005 | <0.05 | <0.01 |
| D2 232314 | | <0.005 | 0.12 | <0.01 | D2 232355 | | <0.005 | <0.05 | <0.01 |
| D2 232315 | | <0.005 | <0.05 | <0.01 | D2 232356 | | <0.005 | <0.05 | <0.01 |
| D2 232316 | | <0.005 | <0.05 | <0.01 | D2 232357 | | <0.005 | <0.05 | <0.01 |
| D2 232317 | | <0.005 | <0.05 | <0.01 | D2 232358 | | <0.005 | <0.05 | <0.01 |
| D2 232318 | | <0.005 | <0.05 | <0.01 | D2 232359 | | <0.005 | 0.10 | <0.01 |
| D2 232319 | | <0.005 | 0.13 | <0.01 | D2 232360 | | <0.005 | <0.05 | <0.01 |
| D2 232320 | | <0.005 | 0.15 | <0.01 | D2 232421 | | <0.005 | <0.05 | <0.01 |
| D2 232321 | | <0.005 | <0.05 | <0.01 | D2 232422 | | <0.005 | <0.05 | <0.01 |
| D2 232322 | | <0.005 | 0.06 | <0.01 | | | | | |
| D2 232323 | | <0.005 | <0.05 | <0.01 | | | | | |
| D2 232324 | | <0.005 | <0.05 | <0.01 | | | | | |
| D2 232325 | | <0.005 | <0.05 | <0.01 | | | | | |
| D2 232326 | | <0.005 | <0.05 | <0.01 | | | | | |
| D2 232327 | | <0.005 | <0.05 | <0.01 | | | | | |
| D2 232328 | | <0.005 | <0.05 | <0.01 | | | | | |
| D2 232329 | | <0.005 | <0.05 | <0.01 | | | | | |
| D2 232330 | | <0.005 | <0.05 | <0.01 | | | | | |
| D2 232331 | | <0.005 | <0.05 | <0.01 | | | | | |
| D2 232332 | | <0.005 | 0.13 | <0.01 | | | | | |
| D2 232333 | | <0.005 | <0.05 | <0.01 | | | | | |
| D2 232334 | | <0.005 | <0.05 | <0.01 | | | | | |
| D2 232335 | | 0.006 | <0.05 | <0.01 | | | | | |
| D2 232336 | | <0.005 | <0.05 | <0.01 | | | | | |
| D2 232337 | | 0.094 | <0.05 | 0.07 | | | | | |
| D2 232338 | | <0.005 | <0.05 | <0.01 | | | | | |
| D2 232339 | | <0.005 | <0.05 | <0.01 | | | | | |
| D2 232340 | | <0.005 | <0.05 | <0.01 | | | | | |

Bondar Clegg Canada Limited

130 Pemberton Avenue, North Vancouver, BC, V7P 2R5, Canada

Tel: (604) 985-0681, Fax: (604) 985-1071

CLIENT: BEAU PRE EXPLORATIONS LTD.
 REPORT: V01-00287.0 (COMPLETE)

PROJECT: VF-2000
 DATE RECEIVED: 19-FEB-01

DATE PRINTED: 26-FEB-01 PAGE 2 OF 3

| STANDARD
NAME | ELEMENT
UNITS | AuGrav
OPT | AgGrav
OPT | As
PCT | STANDARD
NAME | ELEMENT
UNITS | AuGrav
OPT | AgGrav
OPT | As
PCT |
|--------------------|------------------|---------------|---------------|-----------|------------------|------------------|---------------|---------------|-----------|
| OX12 Oxide | | 0.188 | 0.32 | - | | | | | |
| Number of Analyses | | 1 | 1 | - | | | | | |
| Mean Value | | 0.1879 | 0.321 | - | | | | | |
| Standard Deviation | | - | - | - | | | | | |
| Accepted Value | | 0.192 | 0.30 | - | | | | | |
| PD-1 | | - | - | 0.79 | | | | | |
| Number of Analyses | | - | - | 1 | | | | | |
| Mean Value | | - | - | 0.791 | | | | | |
| Standard Deviation | | - | - | - | | | | | |
| Accepted Value | | - | - | 0.77 | | | | | |
| ANALYTICAL BLANK | | <0.005 | <0.05 | - | | | | | |
| Number of Analyses | | 1 | 1 | - | | | | | |
| Mean Value | | 0.0025 | 0.025 | - | | | | | |
| Standard Deviation | | - | - | - | | | | | |
| Accepted Value | | <0.001 | <0.01 | <0.01 | | | | | |
| OX11 Oxide | | 0.090 | 0.77 | - | | | | | |
| Number of Analyses | | 1 | 1 | - | | | | | |
| Mean Value | | 0.0895 | 0.767 | - | | | | | |
| Standard Deviation | | - | - | - | | | | | |
| Accepted Value | | 0.086 | 0.73 | - | | | | | |
| CD-1 | | - | - | 0.70 | | | | | |
| Number of Analyses | | - | - | 1 | | | | | |
| Mean Value | | - | - | 0.698 | | | | | |
| Standard Deviation | | - | - | - | | | | | |
| Accepted Value | | - | - | 0.66 | | | | | |

CLIENT: BEAU PRE EXPLORATIONS LTD.
 REPORT: V01-00287.0 (COMPLETE)

DATE RECEIVED: 19-FEB-01

PROJECT: VF-2000

DATE PRINTED: 26-FEB-01

PAGE 3 OF 3

| SAMPLE NUMBER | ELEMENT UNITS | AuGrav OPT | AgGrav OPT | As PCT | SAMPLE NUMBER | ELEMENT UNITS | AuGrav OPT | AgGrav OPT | As PCT |
|---------------|---------------|------------|------------|--------|---------------|---------------|------------|------------|--------|
| 232301 | <0.005 | <0.05 | <0.01 | | | | | | |
| Duplicate | | | <0.01 | | | | | | |
| 232306 | <0.005 | <0.05 | <0.01 | | | | | | |
| Duplicate | <0.005 | <0.05 | | | | | | | |
| 232310 | <0.005 | <0.05 | 0.02 | | | | | | |
| Duplicate | | | 0.02 | | | | | | |
| 232315 | <0.005 | <0.05 | <0.01 | | | | | | |
| Duplicate | | | <0.01 | | | | | | |
| 232318 | <0.005 | <0.05 | <0.01 | | | | | | |
| Duplicate | <0.005 | <0.05 | | | | | | | |
| 232320 | <0.005 | 0.15 | <0.01 | | | | | | |
| Duplicate | | | <0.01 | | | | | | |
| 232325 | <0.005 | <0.05 | <0.01 | | | | | | |
| Duplicate | | | <0.01 | | | | | | |
| 232329 | <0.005 | <0.05 | <0.01 | | | | | | |
| Duplicate | <0.005 | <0.05 | | | | | | | |
| 232330 | <0.005 | <0.05 | <0.01 | | | | | | |
| Duplicate | | | <0.01 | | | | | | |
| 232334 | <0.005 | <0.05 | <0.01 | | | | | | |
| Duplicate | | | <0.01 | | | | | | |
| 232341 | <0.005 | <0.05 | <0.01 | | | | | | |
| Duplicate | <0.005 | <0.05 | | | | | | | |
| 232343 | <0.005 | <0.05 | <0.01 | | | | | | |
| Duplicate | | | <0.01 | | | | | | |
| 232348 | <0.005 | <0.05 | <0.01 | | | | | | |
| Duplicate | | | <0.01 | | | | | | |
| 232353 | <0.005 | <0.05 | <0.01 | | | | | | |
| Duplicate | <0.005 | <0.05 | | | | | | | |
| 232354 | <0.005 | <0.05 | <0.01 | | | | | | |
| Duplicate | | | <0.01 | | | | | | |
| 232359 | <0.005 | 0.10 | <0.01 | | | | | | |
| Duplicate | | | <0.01 | | | | | | |



BONDAR CLEGG

Vancouver, B.C. Canada

"URGENT & CONFIDENTIAL"

To: BEAU PRE EXPLORATIONS LTD.
 Attention :
 Reference :
 Submitter : UNKNOWN

Our Fax No: (604) 985-1071
 Your Fax No: 1-250-384-6431
 Number of Pages : 4 including this page.

Report : V01-00288.0 Status : PRELIMINARY Total number of samples: 20

| Element Method | | Total | Element Method | | Total | Element Method | | Total |
|----------------|---------------------|-------|----------------|---------------------|-------|----------------|---------------------|-------|
| Ag | INDUC. COUP. PLASMA | 20 | Cu | INDUC. COUP. PLASMA | 20 | Pb | INDUC. COUP. PLASMA | 20 |
| Zn | INDUC. COUP. PLASMA | 20 | Mo | INDUC. COUP. PLASMA | 20 | Ni | INDUC. COUP. PLASMA | 20 |
| Co | INDUC. COUP. PLASMA | 20 | Cd | INDUC. COUP. PLASMA | 20 | Bi | INDUC. COUP. PLASMA | 20 |
| As | INDUC. COUP. PLASMA | 20 | Sb | INDUC. COUP. PLASMA | 20 | Fe | INDUC. COUP. PLASMA | 20 |
| Mn | INDUC. COUP. PLASMA | 20 | Tl | INDUC. COUP. PLASMA | 20 | Ba | INDUC. COUP. PLASMA | 20 |
| Cr | INDUC. COUP. PLASMA | 20 | V | INDUC. COUP. PLASMA | 20 | Sn | INDUC. COUP. PLASMA | 20 |
| W | INDUC. COUP. PLASMA | 20 | La | INDUC. COUP. PLASMA | 20 | Al | INDUC. COUP. PLASMA | 20 |
| Mg | INDUC. COUP. PLASMA | 20 | Ca | INDUC. COUP. PLASMA | 20 | Na | INDUC. COUP. PLASMA | 20 |
| K | INDUC. COUP. PLASMA | 20 | Sr | INDUC. COUP. PLASMA | 20 | Y | INDUC. COUP. PLASMA | 20 |
| Ga | INDUC. COUP. PLASMA | 20 | Li | INDUC. COUP. PLASMA | 20 | Nb | INDUC. COUP. PLASMA | 20 |
| Sc | INDUC. COUP. PLASMA | 20 | Ta | INDUC. COUP. PLASMA | 20 | Tl | INDUC. COUP. PLASMA | 20 |
| Zr | INDUC. COUP. PLASMA | 20 | S | INDUC. COUP. PLASMA | 20 | | | |

Results to follow for: Ag-150 Ag+150 Ag Tot Au (-) Au (+) Au Tot Wt (-) WT (+)

| Sample Preparations | Total | Sample Type | Total | Size Fraction | Total | Remarks |
|---------------------|-------|-------------|-------|---------------|-------|---------|
| CRUSH/SPLIT & PULV. | 20 | DRILL CORE | 20 | +150/-150 | 20 | |
| OVERWEIGHT/KG | 5 | | | | | |
| METALLICS SCREENING | 20 | | | | | |
| | | | | | | |
| | | | | | | |
| | | | | | | |
| | | | | | | |
| | | | | | | |
| | | | | | | |
| | | | | | | |

Notes:

If you do not receive the entire transmission in legible form, please call us at (604) 985-0681.



BONDAR CLEGG

CLIENT: BEAU PRE EXPLORATIONS LTD.

REPORT: V01-00288.0 **** PRELIMINARY ****

DATE RECEIVED: 19-FEB-01

PROJECT: VF-2000

DATE PRINTED: 21-FEB-01

PAGE 1C (3 / 3)

| SAMPLE NUMBER | ELEMENT UNITS | K PCT | Sr PPM | Y PPM | Ga PPM | Li PPM | No PPM | Sc PPM | Ta PPM | Ti PCT | Zr PPM | S PCT |
|---------------|---------------|-------|--------|-------|--------|--------|--------|--------|--------|--------|--------|-------|
| DW 232401 | | 1.20 | 21 | 4 | 8 | 39 | 5 | 8 | <10 | 0.147 | 2 | 0.13 |
| DW 232402 | | 0.98 | 14 | 3 | 6 | 33 | 5 | 6 | <10 | 0.129 | 2 | 0.21 |
| DW 232403 | | 1.45 | 18 | 4 | 8 | 44 | 6 | 7 | <10 | 0.159 | 2 | 0.50 |
| DW 232404 | | 0.79 | 52 | 4 | 5 | 23 | 4 | <5 | <10 | 0.092 | 2 | 0.17 |
| DW 232405 | | 1.52 | 19 | 4 | 8 | 42 | 6 | 7 | <10 | 0.167 | 2 | 0.53 |
| DW 232406 | | 1.27 | 25 | 4 | 8 | 39 | 5 | 6 | <10 | 0.132 | 2 | 0.37 |
| DW 232407 | | 0.83 | 27 | 5 | 6 | 28 | 4 | 6 | <10 | 0.111 | 2 | 0.12 |
| DW 232408 | | 1.47 | 31 | 5 | 8 | 31 | 5 | 7 | <10 | 0.214 | 2 | 0.25 |
| DW 232409 | | 1.44 | 57 | 5 | 7 | 29 | 5 | 7 | <10 | 0.211 | 2 | 0.27 |
| DW 232410 | | 1.33 | 27 | 4 | 6 | 27 | 5 | 7 | <10 | 0.213 | 2 | 0.20 |
| DW 232411 | | 1.39 | 32 | 5 | 8 | 28 | 4 | 7 | <10 | 0.227 | 2 | 0.23 |
| DW 232412 | | 1.40 | 30 | 6 | 8 | 30 | 5 | 9 | <10 | 0.217 | 2 | 0.18 |
| DW 232413 | | 1.06 | 28 | 6 | 5 | 26 | 3 | <5 | <10 | 0.164 | 2 | 0.10 |
| DW 232414 | | 1.22 | 75 | 7 | 7 | 31 | 5 | 7 | <10 | 0.190 | 2 | 0.19 |
| DW 232415 | | 1.28 | 76 | 5 | 7 | 29 | 5 | 7 | <10 | 0.216 | 2 | 0.24 |
| DW 232416 | | 1.39 | 49 | 5 | 7 | 27 | 5 | 8 | <10 | 0.220 | 2 | 0.29 |
| DW 232417 | | 1.48 | 36 | 6 | 11 | 27 | 6 | 8 | <10 | 0.249 | 2 | 0.91 |
| DW 232418 | | 0.83 | 68 | 5 | 6 | 27 | 4 | 5 | <10 | 0.149 | 2 | 0.33 |
| DW 232419 | | 1.11 | 28 | 6 | 6 | 30 | 4 | 5 | <10 | 0.196 | 2 | 0.24 |
| DW 232420 | | 1.29 | 63 | 5 | 7 | 37 | 5 | 6 | <10 | 0.170 | 2 | 0.21 |



BONDAR CLEGG

CLIENT: BEAU PRE EXPLORATIONS LTD.

REPORT: V01-00288.0 **** PRELIMINARY ****

DATE RECEIVED: 19-FEB-01

PROJECT: VF-2000

DATE PRINTED: 21-FEB-01

PAGE 1A (1 / 3)

| SAMPLE NUMBER | ELEMENT UNITS | Ag PPM | Cu PPM | Pb PPM | Zn PPM | Mo PPM | Ni PPM | Co PPM | Cd PPM | Bi PPM | As PPM | Sb PPM | Fe PCT |
|---------------|---------------|--------|--------|--------|--------|--------|--------|--------|--------|--------|--------|--------|--------|
| DW 232401 | | <0.2 | 34 | <2 | 52 | 2 | 35 | 15 | <0.2 | <5 | 7 | <5 | 3.67 |
| DW 232402 | | <0.2 | 28 | <2 | 51 | 2 | 27 | 13 | <0.2 | <5 | <5 | <5 | 3.29 |
| DW 232403 | | <0.2 | 53 | <2 | 97 | <1 | 45 | 18 | <0.2 | <5 | 271 | <5 | 4.35 |
| DW 232404 | | <0.2 | 14 | <2 | 47 | 5 | 18 | 8 | <0.2 | <5 | 694 | <5 | 2.26 |
| DW 232405 | | 0.4 | 54 | <2 | 103 | 1 | 46 | 18 | 0.2 | <5 | 9 | <5 | 4.67 |
| DW 232406 | | <0.2 | 50 | <2 | 76 | 2 | 47 | 18 | <0.2 | <5 | 7 | <5 | 4.55 |
| DW 232407 | | <0.2 | 18 | <2 | 61 | 2 | 25 | 12 | <0.2 | <5 | <5 | <5 | 2.91 |
| DW 232408 | | <0.2 | 31 | <2 | 77 | 2 | 28 | 15 | <0.2 | <5 | <5 | <5 | 3.32 |
| DW 232409 | | <0.2 | 29 | <2 | 74 | 1 | 28 | 14 | <0.2 | <5 | <5 | <5 | 3.29 |
| DW 232410 | | <0.2 | 19 | <2 | 68 | 2 | 23 | 13 | <0.2 | <5 | <5 | <5 | 3.10 |
| DW 232411 | | <0.2 | 20 | <2 | 72 | 2 | 25 | 14 | <0.2 | <5 | <5 | <5 | 3.23 |
| DW 232412 | | <0.2 | 19 | <2 | 73 | 2 | 25 | 15 | <0.2 | <5 | 32 | <5 | 3.37 |
| DW 232413 | | <0.2 | 11 | <2 | 62 | 2 | 24 | 12 | <0.2 | <5 | 29 | <5 | 2.64 |
| DW 232414 | | <0.2 | 20 | <2 | 69 | 3 | 23 | 13 | <0.2 | <5 | 40 | <5 | 3.28 |
| DW 232415 | | <0.2 | 21 | <2 | 66 | 2 | 25 | 14 | <0.2 | <5 | 17 | <5 | 3.26 |
| DW 232416 | | <0.2 | 25 | <2 | 67 | 3 | 25 | 15 | <0.2 | <5 | 19 | <5 | 3.35 |
| DW 232417 | | <0.2 | 44 | <2 | 81 | 2 | 35 | 18 | 0.2 | 6 | 5 | <5 | 4.29 |
| DW 232418 | | <0.2 | 17 | <2 | 60 | 5 | 20 | 10 | <0.2 | <5 | 5 | <5 | 2.54 |
| DW 232419 | | <0.2 | 14 | <2 | 68 | 2 | 23 | 12 | <0.2 | <5 | 6 | <5 | 2.97 |
| DW 232420 | | <0.2 | 26 | <2 | 73 | 2 | 26 | 14 | <0.2 | <5 | 9 | <5 | 3.39 |



BONDAR CLEGG

CLIENT: BEAU PRE EXPLORATIONS LTD.

REPORT: V01-00288.0 **** PRELIMINARY ****

DATE RECEIVED: 19-FEB-01

PROJECT: VF-2000

DATE PRINTED: 21-FEB-01

PAGE 1B (2 / 3)

| AMPLE
NUMBER | ELEMENT
UNITS | Mn
PPM | TE
PPM | Ba
PPM | Cr
PPM | V
PPM | Sn
PPM | W
PPM | La
PPM | Al
PCT | Mg
PCT | Ca
PCT | Na
PCT |
|-----------------|------------------|-----------|-----------|-----------|-----------|----------|-----------|----------|-----------|-----------|-----------|-----------|-----------|
| DW 232401 | | 328 | <10 | 324 | 154 | 94 | <20 | <20 | 11 | 2.95 | 1.23 | 0.22 | 0.10 |
| DW 232402 | | 314 | <10 | 221 | 114 | 79 | <20 | <20 | 11 | 2.54 | 1.11 | 0.20 | 0.09 |
| DW 232403 | | 336 | <10 | 285 | 113 | 92 | <20 | <20 | 9 | 2.95 | 1.34 | 0.26 | 0.09 |
| DW 232404 | | 244 | <10 | 218 | 202 | 55 | <20 | 89 | 4 | 2.44 | 0.68 | 0.63 | 0.22 |
| DW 232405 | | 411 | <10 | 272 | 104 | 90 | <20 | <20 | 8 | 2.86 | 1.37 | 0.30 | 0.07 |
| DW 232406 | | 455 | <10 | 247 | 122 | 82 | <20 | <20 | 9 | 2.76 | 1.37 | 0.58 | 0.06 |
| DW 232407 | | 300 | <10 | 255 | 133 | 81 | <20 | <20 | 10 | 2.29 | 1.08 | 0.63 | 0.13 |
| DW 232408 | | 470 | <10 | 475 | 101 | 82 | <20 | <20 | 7 | 2.68 | 1.13 | 0.50 | 0.12 |
| DW 232409 | | 471 | <10 | 421 | 132 | 81 | <20 | <20 | 6 | 2.63 | 1.10 | 0.80 | 0.16 |
| DW 232410 | | 404 | <10 | 366 | 98 | 79 | <20 | <20 | 6 | 2.25 | 0.99 | 0.43 | 0.11 |
| DW 232411 | | 433 | <10 | 393 | 103 | 82 | <20 | <20 | 7 | 2.40 | 1.04 | 0.54 | 0.13 |
| DW 232412 | | 432 | <10 | 456 | 123 | 92 | <20 | <20 | 9 | 2.60 | 1.11 | 0.37 | 0.17 |
| DW 232413 | | 421 | <10 | 276 | 143 | 62 | <20 | <20 | 7 | 2.07 | 0.92 | 0.79 | 0.11 |
| DW 232414 | | 431 | <10 | 352 | 137 | 82 | <20 | <20 | 8 | 2.77 | 1.08 | 1.05 | 0.14 |
| DW 232415 | | 395 | <10 | 501 | 139 | 93 | <20 | <20 | 5 | 2.81 | 1.10 | 1.02 | 0.22 |
| DW 232416 | | 448 | <10 | 435 | 137 | 87 | <20 | <20 | 5 | 2.53 | 1.13 | 0.92 | 0.16 |
| DW 232417 | | 587 | <10 | 111 | 129 | 127 | <20 | <20 | 4 | 2.49 | 1.34 | 1.71 | 0.13 |
| DW 232418 | | 342 | <10 | 278 | 182 | 66 | <20 | <20 | 6 | 2.21 | 0.86 | 0.89 | 0.16 |
| DW 232419 | | 400 | <10 | 240 | 136 | 71 | <20 | <20 | 7 | 2.16 | 0.94 | 0.30 | 0.09 |
| DW 232420 | | 425 | <10 | 345 | 121 | 84 | <20 | <20 | 7 | 2.85 | 1.16 | 0.86 | 0.17 |



BONDAR CLEGG

CLIENT: BEAU PRE EXPLORATIONS LTD.

PROJECT: NONE GIVEN

REPORT: V01-00122.0 (COMPLETE)

DATE RECEIVED: 26-JAN-01

DATE PRINTED: 8-FEB-01

PAGE 1A (1 / 4)

| SAMPLE
NUMBER | ELEMENT
UNITS | Wt (-)
g | WT (+)
g | Au (-)
OPT | Au (+)
OPT | Au Tot
OPT | Ag-150
OPT | Ag+150
OPT | Ag Tot
OPT | Ag
PPM | Cu
PPM | Pb
PPM | Zn
PPM |
|------------------|------------------|-------------|-------------|---------------|---------------|---------------|---------------|---------------|---------------|-----------|-----------|-----------|-----------|
| W REEF C | | 1038.0 | 44.11 | 27.110 | 1070.54 | 69.644 | 2.13 | 87.1 | 5.60 | 70.0 | 66 | 717 | 24 |



BONDAR CLEGG

CLIENT: BEAU PRE EXPLORATIONS LTD.
 REPORT: V01-00122.0 (COMPLETE)

PROJECT: NONE GIVEN

DATE PRINTED: 8-FEB-01

PAGE 1B (2 / 4)

| SAMPLE NUMBER | ELEMENT UNITS | Mo PPM | Ni PPM | Co PPM | Cd PPM | Bi PPM | As PPM | Sb PPM | Fe PCT | Mn PPM | TE PPM | Ba PPM | Cr PPM |
|---------------|---------------|--------|--------|--------|--------|--------|--------|--------|--------|--------|--------|--------|--------|
| ZW REEF C | 7 | 35 | 14 | 105.4 | <5 | >10000 | 15 | 4.39 | 110 | <10 | 61 | 177 | |



BONDAR CLEGG

CLIENT: BEAU PRE EXPLORATIONS LTD.

REPORT: V01-00122.0 (COMPLETE)

DATE RECEIVED: 26-JAN-01

PROJECT: NONE GIVEN

DATE PRINTED: 8-FEB-01

PAGE 1C (3 / 4)

| SAMPLE NUMBER | ELEMENT UNITS | V
PPM | Sn
PPM | W
PPM | La
PPM | Al
PCT | Mg
PCT | Ca
PCT | Na
PCT | K
PCT | Sr
PPM | Y
PPM | Ga
PPM |
|---------------|---------------|----------|-----------|----------|-----------|-----------|-----------|-----------|-----------|----------|-----------|----------|-----------|
| W REEF C | | 28 | <20 | <20 | 1 | 1.00 | 0.33 | 0.34 | 0.08 | 0.36 | 23 | 2 | 2 |



BONDAR CLEGG

CLIENT: BEAU PRE EXPLORATIONS LTD.

REPORT: V01-00122.0 (COMPLETE)

PROJECT: NONE GIVEN

DATE PRINTED: 8-FEB-01

PAGE 1D(4 / 4)

| SAMPLE NUMBER | ELEMENT UNITS | Li PPM | Nb PPM | Sc PPM | Ta PPM | Ti PCT | Zr PPM | S PCT |
|---------------|---------------|--------|--------|--------|--------|--------|--------|-------|
| W REEF C | 6 | <1 | <5 | <10 | 0.049 | <1 | 1.97 | |



BONDAR CLEGG

11 GRAB
C REEF

Vancouver, B.C. Canada

"URGENT & CONFIDENTIAL"

To: BEAU PRE EXPLORATIONS LTD.
 Attention :
 Reference :
 Submitter : UNKNOWN

Our Fax No: (604) 985-1071
 Your Fax No: 1-250-384-6431
 Number of Pages : 5 including this page.

Report : V01-00122.0

Status : COMPLETE

Total number of samples: 1

| Element Method | Total | Element Method | Total | Element Method | Total |
|------------------------|-------|------------------------|-------|------------------------|-------|
| Wt (-) FIRE ASSAY | 1 | WT (+) FIRE ASSAY | 1 | Au (-) FIRE ASSAY | 1 |
| Au (+) FIRE ASSAY | 1 | Au Tot FIRE ASSAY | 1 | Ag-150 FIRE ASSAY | 1 |
| Ag+150 FIRE ASSAY | 1 | Ag Tot FIRE ASSAY | 1 | Ag INDUC. COUP. PLASMA | 1 |
| Cu INDUC. COUP. PLASMA | 1 | Pb INDUC. COUP. PLASMA | 1 | Zn INDUC. COUP. PLASMA | 1 |
| Mo INDUC. COUP. PLASMA | 1 | Ni INDUC. COUP. PLASMA | 1 | Co INDUC. COUP. PLASMA | 1 |
| Cd INDUC. COUP. PLASMA | 1 | Bi INDUC. COUP. PLASMA | 1 | As INDUC. COUP. PLASMA | 1 |
| Sb INDUC. COUP. PLASMA | 1 | Fe INDUC. COUP. PLASMA | 1 | Mn INDUC. COUP. PLASMA | 1 |
| TE INDUC. COUP. PLASMA | 1 | Ba INDUC. COUP. PLASMA | 1 | Cr INDUC. COUP. PLASMA | 1 |
| V INDUC. COUP. PLASMA | 1 | Sn INDUC. COUP. PLASMA | 1 | W INDUC. COUP. PLASMA | 1 |
| La INDUC. COUP. PLASMA | 1 | Al INDUC. COUP. PLASMA | 1 | Mg INDUC. COUP. PLASMA | 1 |
| Ca INDUC. COUP. PLASMA | 1 | Na INDUC. COUP. PLASMA | 1 | K INDUC. COUP. PLASMA | 1 |
| Sr INDUC. COUP. PLASMA | 1 | Y INDUC. COUP. PLASMA | 1 | Ga INDUC. COUP. PLASMA | 1 |
| Li INDUC. COUP. PLASMA | 1 | Nb INDUC. COUP. PLASMA | 1 | Sc INDUC. COUP. PLASMA | 1 |
| Ta INDUC. COUP. PLASMA | 1 | Ti INDUC. COUP. PLASMA | 1 | Zr INDUC. COUP. PLASMA | 1 |
| S INDUC. COUP. PLASMA | 1 | | | | |

| Sample Preparations | Total | Sample Type | Total | Size Fraction | Total | Remarks |
|---------------------|-------|-------------|-------|---------------|-------|---|
| CRUSH ONLY | 1 | ROCK | 1 | +150/-150 | 1 | High std for As is due to carry over. ION |
| PULVERIZATION | 1 | | | | | |
| METALLICS SCREENING | 1 | | | | | |

Notes:

If you do not receive the entire transmission in legible form, please call us at (604) 985-0681.



BONDAR CLEGG



Geochemical
Lab
Report

BEAU PRE EXPLORATIONS LTD.
#108-3930 SHELBURNE ST.
VICTORIA, B.C.
V8P 5P6

Received from Beau Pre Explorations Ltd.
on 1st Oct 1993
KDS
M. McLean



BONDAR CLEGG



**Geochemical
Lab
Report**

REPORT: V00-02176.0 (COMPLETE)

REFERENCE:

CLIENT: BEAU PRE EXPLORATIONS LTD.

SUBMITTED BY: UNKNOWN

PROJECT: VAL/KDS2

DATE RECEIVED: 24-NOV-00

DATE PRINTED: 30-NOV-00

| APPROVED | DATE | ORDER | ELEMENT | NUMBER OF ANALYSES | LOWER DETECTION LIMIT | EXTRACTION | METHOD |
|--------------|--------|--------|------------------------------|--------------------|-----------------------|---------------------|---------------------|
| | 001125 | 1 | Wt (-) Pulp Wt. Minus Fract. | 3 | g | | FIRE ASSAY |
| | 001125 | 2 | WT (+) Pulp wt. Plus Fract | 3 | 0.01 g | | FIRE ASSAY |
| | 001125 | 3 | Au (-) Gold. Minus Fraction | 3 | 0.001 OPT | | FIRE ASSAY |
| | 001125 | 4 | Au (+) Gold. Plus Fraction | 3 | 0.01 OPT | | FIRE ASSAY |
| | 001125 | 5 | Au Tot Gold in total sample | 3 | 0.001 OPT | | FIRE ASSAY |
| | 001125 | 6 | Ag-150 Silver Avg-150 mesh. | 3 | 0.02 OPT | | FIRE ASSAY |
| | 001125 | 7 | Ag+150 Silver in +150 mesh. | 3 | 0.02 OPT | | FIRE ASSAY |
| | 001125 | 8 | Ag Tot Ag in total sample. | 3 | 0.02 OPT | | FIRE ASSAY |
| | 001125 | 9 | As As - IC01 | 3 | 5 PPM | HCL:HNO3 (3:1) | INDUC. COUP. PLASMA |
| | 001125 | 10 | Fe Fe - IC01 | 3 | 0.01 PCT | HCL:HNO3 (3:1) | INDUC. COUP. PLASMA |
| | 001125 | 11 | S S - IC01 | 3 | 0.002 PCT | HCL:HNO3 (3:1) | INDUC. COUP. PLASMA |
| SAMPLE TYPES | | NUMBER | SIZE FRACTIONS | | NUMBER | SAMPLE PREPARATIONS | NUMBER |
| R ROCK | | 3 | 2 | -150 | 3 | CRUSH/SPLIT & PULV. | 3 |
| | | | | | | OVERWEIGHT/KG | 2 |
| | | | | | | METALLICS SCREENING | 3 |

REPORT COPIES TO: #108-3930 SHELBURNE ST.

INVOICE TO: #108-3930 SHELBURNE ST.

 This report must not be reproduced except in full. The data presented in this report is specific to those samples identified under "Sample Number" and is applicable only to the samples as received expressed on a dry basis unless otherwise indicated



BONDAR CLEGG



VANCOUVER BRANCH

Geochemical
Lab
Report

CLIENT: BEAU PRE EXPLORATIONS LTD.

REPORT: V00-02176.0 (COMPLETE)

DATE RECEIVED: 24-NOV-00

PROJECT: VAL/KDS2

DATE PRINTED: 30-NOV-00

PAGE 1 OF 2

| SAMPLE
NUMBER | ELEMENT
UNITS | Wt (-)
g | WT (+)
g | Au (-)
OPT | Au (+)
OPT | Au Tot
OPT | Ag-150
OPT | Ag+150
OPT | Ag Tot
OPT | As
PPM | Fe
PCT | S
PCT |
|------------------|------------------|-------------|-------------|---------------|---------------|---------------|---------------|---------------|---------------|-----------|-----------|----------|
| R2 232251 | | 201.4 | 22.72 | 0.091 | 2.01 | 0.286 | <0.02 | <0.02 | <0.02 | 2860 | 2.13 | 0.373 |
| R2 232252 | | 257.0 | 22.91 | 0.154 | 2.17 | 0.319 | 0.03 | 0.20 | 0.05 | 3069 | 2.20 | 0.391 |
| R2 232253 | | 222.6 | 21.95 | 1.213 | 17.66 | 2.689 | 0.13 | 1.56 | 0.26 | 4522 | 2.30 | 0.467 |



BONDAR CLEGG



**Geochemical
Lab
Report**

CLIENT: BEAU PRE EXPLORATIONS LTD.

REPORT: V00-02176.0 (COMPLETE)

DATE RECEIVED: 24-NOV-00

PROJECT: VAL/KDS2

DATE PRINTED: 30-NOV-00

PAGE 2 OF 2

| STANDARD
NAME | ELEMENT
UNITS | WT (-)
g | WT (+)
g | Au (-)
OPT | Au (+)
OPT | Au Tot
OPT | Ag-150
OPT | Ag+150
OPT | Ag Tot
OPT | As
PPM | Fe
PCT | S
PCT |
|--------------------|------------------|-------------|-------------|---------------|---------------|---------------|---------------|---------------|---------------|-----------|-----------|----------|
| ANALYTICAL BLANK | | - | - | <0.001 | - | - | <0.02 | - | - | <5 | <0.01 | <0.002 |
| Number of Analyses | | - | - | 1 | - | - | 1 | - | - | 1 | 1 | 1 |
| Mean Value | | - | - | 0.0004 | - | - | 0.010 | - | - | 2.5 | 0.005 | 0.0010 |
| Standard Deviation | | - | - | - | - | - | - | - | - | - | - | - |
| Accepted Value | | <0.1 | <0.01 | <0.001 | <0.01 | <0.001 | <0.01 | <0.01 | <0.01 | <1 | <0.01 | <0.001 |
| OX11 Oxide | | - | 31.34 | 0.090 | 0.09 | - | 0.74 | 0.69 | - | - | - | - |
| Number of Analyses | | - | 1 | 1 | 1 | - | 1 | 1 | - | - | - | - |
| Mean Value | | - | 31.340 | 0.0901 | 0.086 | - | 0.744 | 0.688 | - | - | - | - |
| Standard Deviation | | - | - | - | - | - | - | - | - | - | - | - |
| Accepted Value | | - | - | 0.086 | - | - | - | - | - | - | - | - |
| CANMET LKSD-2 | | - | - | - | - | - | - | - | - | 10 | 3.45 | 0.168 |
| Number of Analyses | | - | - | - | - | - | - | - | - | 1 | 1 | 1 |
| Mean Value | | - | - | - | - | - | - | - | - | 10.4 | 3.448 | 0.1684 |
| Standard Deviation | | - | - | - | - | - | - | - | - | - | - | - |
| Accepted Value | | - | - | - | - | - | - | - | - | 9 | 3.50 | - |

Bondar Clegg Canada Limited

130 Pemberton Avenue, North Vancouver, BC, V7P 2R5, Canada

Tel: (604) 985-0681, Fax: (604) 985-1071



BONDAR CLEGG



Geochemical
Lab
Report

BEAU PRE EXPLORATIONS LTD.
#108-3930 SHELBURNE ST.
VICTORIA, B.C.
V8P 5P6

Head grade

+ + + +

82



BONDAR CLEGG



Geochemical Lab Report

REPORT: V00-02176.0 (COMPLETE)

REFERENCE:

CLIENT: BEAU PRE EXPLORATIONS LTD.
PROJECT: VAL/KDS2

SUBMITTED BY: UNKNOWN

DATE RECEIVED: 24-NOV-00

DATE PRINTED: 30-NOV-00

| DATE APPROVED | ORDER | ELEMENT | NUMBER OF ANALYSES | LOWER DETECTION LIMIT | EXTRACTION | METHOD |
|---------------|-------|------------------------------|--------------------|-----------------------|----------------|----------------------------|
| 001125 | 1 | Wt (-) Pulp Wt. Minus Fract. | 3 | g | | FIRE ASSAY |
| 001125 | 2 | WT (+) Pulp wt. Plus Fract | 3 | 0.01 g | | FIRE ASSAY |
| 001125 | 3 | Au (-) Gold. Minus Fraction | 3 | 0.001 OPT | | FIRE ASSAY |
| 001125 | 4 | Au (+) Gold. Plus Fraction | 3 | 0.01 OPT | | FIRE ASSAY |
| 001125 | 5 | Au Tot Gold in total sample | 3 | 0.001 OPT | | FIRE ASSAY |
| 001125 | 6 | Ag-150 Silver Avg-150 mesh. | 3 | 0.02 OPT | | FIRE ASSAY |
| 001125 | 7 | Ag+150 Silver in +150 mesh. | 3 | 0.02 OPT | | FIRE ASSAY |
| 001125 | 8 | Ag Tot Ag in total sample. | 3 | 0.02 OPT | | FIRE ASSAY |
| 001125 | 9 | As As - IC01 | 3 | 5 PPM | HCL:HNO3 (3:1) | INDUC. COUP. PLASMA |
| 001125 | 10 | Fe Fe - IC01 | 3 | 0.01 PCT | HCL:HNO3 (3:1) | INDUC. COUP. PLASMA |
| 001125 | 11 | S S - IC01 | 3 | 0.002 PCT | HCL:HNO3 (3:1) | INDUC. COUP. PLASMA |
| SAMPLE TYPES | | | NUMBER | SIZE FRACTIONS | NUMBER | SAMPLE PREPARATIONS NUMBER |
| R ROCK | | | 3 | 2 -150 | 3 | CRUSH/SPLIT & PULV. 3 |
| | | | | | | OVERWEIGHT/KG 2 |
| | | | | | | METALLICS SCREENING 3 |

REPORT COPIES TO: #108-3930 SHELBURNE ST.

INVOICE TO: #108-3930 SHELBURNE ST.

This report must not be reproduced except in full. The data presented in this report is specific to those samples identified under "Sample Number" and is applicable only to the samples as received expressed on a dry basis unless otherwise indicated



BONDAR CLEGG

Geochemical
Lab
Report

CLIENT: BEAU PRE EXPLORATIONS LTD.

REPORT: V00-02176.0 (COMPLETE)

DATE RECEIVED: 24-NOV-00

PROJECT: VAL/KDS2

DATE PRINTED: 30-NOV-00

PAGE 1 OF 2

| SAMPLE
NUMBER | ELEMENT
UNITS | Wt (-)
g | WT (+)
g | Au (-)
OPT | Au (+)
OPT | Au Tot
OPT | Ag-150
OPT | Ag+150
OPT | Ag Tot
OPT | As
PPM | Fe
PCT | S
PCT |
|------------------|------------------|-------------|-------------|---------------|---------------|---------------|---------------|---------------|---------------|-----------|-----------|----------|
| R2 232251 | | 201.4 | 22.72 | 0.091 | 2.01 | 0.286 | <0.02 | <0.02 | <0.02 | 2860 | 2.13 | 0.373 |
| R2 232252 | | 257.0 | 22.91 | 0.154 | 2.17 | 0.319 | 0.03 | 0.20 | 0.05 | 3069 | 2.20 | 0.391 |
| R2 232253 | | 222.6 | 21.95 | 1.213 | 17.66 | 2.689 | 0.13 | 1.56 | 0.26 | 4522 | 2.30 | 0.467 |

Bondar Clegg Canada Limited

130 Pemberton Avenue, North Vancouver, BC, V7P 2R5, Canada

Tel: (604) 985-0681, Fax: (604) 985-1071

CLIENT: BEAU PRE EXPLORATIONS LTD.

REPORT: V00-02176.0 (COMPLETE)

DATE RECEIVED: 24-NOV-00

PROJECT: VAL/KDS2

DATE PRINTED: 30-NOV-00

PAGE 2 OF 2

| STANDARD
NAME | ELEMENT
UNITS | Wt (-)
g | WT (+)
g | Au (-)
OPT | Au (+)
OPT | Au Tot
OPT | Ag-150
OPT | Ag+150
OPT | Ag Tot
OPT | As
PPM | Fe
PCT | S
PCT |
|--------------------|------------------|-------------|-------------|---------------|---------------|---------------|---------------|---------------|---------------|-----------|-----------|----------|
| ANALYTICAL BLANK | | - | - | <0.001 | - | - | <0.02 | - | - | <5 | <0.01 | <0.002 |
| Number of Analyses | | - | - | 1 | - | - | 1 | - | - | 1 | 1 | 1 |
| Mean Value | | - | - | 0.0004 | - | - | 0.010 | - | - | 2.5 | 0.005 | 0.0010 |
| Standard Deviation | | - | - | - | - | - | - | - | - | - | - | - |
| Accepted Value | <0.1 | <0.01 | <0.001 | <0.01 | <0.001 | <0.001 | <0.01 | <0.01 | <0.01 | <1 | <0.01 | <0.001 |
| OX11 Oxide | | 31.34 | 0.090 | 0.09 | - | 0.74 | 0.69 | - | - | - | - | - |
| Number of Analyses | | - | 1 | 1 | 1 | - | 1 | 1 | - | - | - | - |
| Mean Value | | - | 31.340 | 0.0901 | 0.086 | - | 0.744 | 0.688 | - | - | - | - |
| Standard Deviation | | - | - | - | - | - | - | - | - | - | - | - |
| Accepted Value | - | - | 0.086 | - | - | - | - | - | - | - | - | - |
| CANMET LKSD-2 | | - | - | - | - | - | - | - | - | 10 | 3.45 | 0.168 |
| Number of Analyses | | - | - | - | - | - | - | - | - | 1 | 1 | 1 |
| Mean Value | | - | - | - | - | - | - | - | - | 10.4 | 3.448 | 0.1684 |
| Standard Deviation | | - | - | - | - | - | - | - | - | - | - | - |
| Accepted Value | - | - | - | - | - | - | - | - | - | 9 | 3.50 | - |



BONDAR CLEGG



Certificate
of
Analysis

BEAU PRE EXPLORATIONS LTD.
#108-3930 SHELBURNE ST.
VICTORIA, B.C.
V8P 5P6

*Poison sample
of Palpithru KDS marked*

BC

BONDAR CLEGG



Certificate of Analysis

REPORT: V00-01837.7 (COMPLETE)

REFERENCE:

CLIENT: BEAU PRE EXPLORATIONS LTD.

SUBMITTED BY: UNKNOWN

PROJECT: NONE GIVEN

DATE RECEIVED: 27-SEP-00

DATE PRINTED: 18-OCT-00

| APPROVED | DATE ORDER | ELEMENT | NUMBER OF | LOWER | | METHOD |
|---------------|------------|-------------------|----------------|-----------------|------------|----------------------------|
| | | | ANALYSES | DETECTION LIMIT | EXTRACTION | |
| | 001017 1 | Au Gold Control | 1 | 0.002 OPT | | FIRE ASSAY |
| | 001017 2 | Ag Silver Control | 1 | 0.02 OPT | | FIRE ASSAY |
| SAMPLE TYPES | | NUMBER | SIZE FRACTIONS | | NUMBER | SAMPLE PREPARATIONS NUMBER |
| C CONCENTRATE | | 1 | 4 AS RECEIVED | | 1 | PULVERIZATION 1 |
| | | | | | | TRANS FROM POLY BAG 1 |
| | | | | | | TOO WET TO CRUSH 1 |

REPORT COPIES TO: #108-3930 SHELBOURNE ST.

INVOICE TO: #108-3930 SHELBOURNE ST.

This report must not be reproduced except in full. The data presented in this report is specific to those samples identified under "Sample Number" and is applicable only to the samples as received expressed on a dry basis unless otherwise indicated

BC

BONDAR CLEGG

**Certificate
of
Analysis**CLIENT: BEAU PRE EXPLORATIONS LTD.
REPORT: V00-01837.7 (COMPLETE)

DATE RECEIVED: 27-SEP-00


PROJECT: NONE GIVEN
DATE PRINTED: 18-OCT-00

PAGE 1 DE 1

| SAMPLE
NUMBER | ELEMENT
UNITS | AU
OPT | Ag
OPT |
|------------------|------------------|-----------|-----------|
|------------------|------------------|-----------|-----------|

| | | |
|-----------|---------|-------|
| C4 V22664 | 495.229 | 94.12 |
|-----------|---------|-------|

Bondar Clegg Canada Limited
130 Pemberton Avenue, North Vancouver, BC, V7P 2R5, Canada
Tel: (604) 985-0681, Fax: (604) 985-1071


Registered Assayer, Province of British Columbia



BONDAR CLEGG



VANCOUVER BRANCH

Geochemical
Lab
Report

GRAB C 1/1

REPORT: V01-00122.0 (COMPLETE)

REFERENCE:

CLIENT: BEAU PRE EXPLORATIONS LTD.

SUBMITTED BY: UNKNOWN

PROJECT: NONE GIVEN

DATE RECEIVED: 26-JAN-01

DATE PRINTED: 9-FEB-01

| APPROVED | ORDER | ELEMENT | DATE | NUMBER OF | LOWER | EXTRACTION | METHOD |
|----------|-------|---------|-----------|-----------|-----------------|----------------|---------------------|
| | | | | ANALYSES | DETECTION LIMIT | | |
| 010130 | 38 | Nb | Nb - IC01 | 1 | 1 PPM | HCL:HNO3 (3:1) | INDUC. COUP. PLASMA |
| 010130 | 39 | Sc | Sc - IC01 | 1 | 5 PPM | HCL:HNO3 (3:1) | INDUC. COUP. PLASMA |
| 010130 | 40 | Ta | Ta - IC01 | 1 | 10 PPM | HCL:HNO3 (3:1) | INDUC. COUP. PLASMA |
| 010130 | 41 | Ti | Ti - IC01 | 1 | 0.010 PCT | HCL:HNO3 (3:1) | INDUC. COUP. PLASMA |
| 010130 | 42 | Zr | Zr - IC01 | 1 | 1 PPM | HCL:HNO3 (3:1) | INDUC. COUP. PLASMA |
| 010130 | 43 | S | S - IC01 | 1 | 0.01 PCT | HCL:HNO3 (3:1) | INDUC. COUP. PLASMA |

| SAMPLE TYPES | NUMBER | SIZE FRACTIONS | NUMBER | SAMPLE PREPARATIONS | NUMBER |
|--------------|--------|----------------|--------|---------------------|--------|
| R ROCK | 1 | W +150/-150 | 1 | CRUSH ONLY | 1 |
| | | | | PULVERIZATION | 1 |
| | | | | METALLICS SCREENING | 1 |

X REMARKS: High std for As is due to carry over. LON

REPORT COPIES TO: #108-3930 SHELBONUE ST.

INVOICE TO: #108-3930 SHELBONUE ST.

This report must not be reproduced except in full. The data presented in this report is specific to those samples identified under "Sample Number" and is applicable only to the samples as received expressed on a dry basis unless otherwise indicated



BONDAR CLEGG



"C Legg"

Geochemical Lab Report

CLIENT: BEAU PRE EXPLORATIONS LTD.

REPORT: V01-00122.0 (COMPLETE)

DATE RECEIVED: 26-JAN-01

PROJECT: NONE GIVEN

DATE PRINTED: 9-FEB-01

PAGE 1A(1/ 8)

| SAMPLE NUMBER | ELEMENT | WT (-) | WT (+) | Au (-) | Au (+) | Au Tot | Ag-150 | Ag+150 | Ag Tot | Ag | Cu | Pb | Zn |
|---------------|---------|--------|--------|--------|---------|--------|--------|--------|--------|------|-----|-----|-----|
| | UNITS | g | g | OPT | OPT | OPT | OPT | OPT | OPT | PPM | PPM | PPM | PPM |
| RW REEF C | | 1038.0 | 44.11 | 27.110 | 1070.54 | 69.644 | 2.13 | 87.1 | 5.60 | 70.0 | 66 | 717 | 24 |



BONDAR CLEGG



VANCOUVER BRANCH

Geochemical Lab Report

CLIENT: BEAU PRE EXPLORATIONS LTD.
REPORT: V01-00122.0 (COMPLETE)

PROJECT: NONE GIVEN

DATE RECEIVED: 26-JAN-01

DATE PRINTED: 9-FEB-01

PAGE 1B(2 / 3)

| SAMPLE NUMBER | ELEMENT UNITS | Mo PPM | Ni PPM | Co PPM | Cd PPM | Bi PPM | As PPM | Sb PPM | Fe PCT | Mn PPM | TE PPM | Ba PPM | Cr PPM |
|---------------|---------------|--------|--------|--------|--------|--------|--------|--------|--------|--------|--------|--------|--------|
| W REEF C | | 7 | 35 | 14 | 105.4 | <5 | >10000 | 15 | 4.39 | 110 | <10 | 61 | 177 |



BONDAR CLEGG

Geochemical
Lab
Report

CLIENT: BEAU PRE EXPLORATIONS LTD.

PROJECT: NONE GIVEN

REPORT: V01-00122.0 (COMPLETE)

DATE RECEIVED: 26-JAN-01

DATE PRINTED: 9-FEB-01

PAGE 10 (3 / 8)

| SAMPLE NUMBER | ELEMENT UNITS | V PPM | Sn PPM | W PPM | La PPM | Al PCT | Mg PCT | Ca PCT | Na PCT | K PCT | Sr PPM | Y PPM | Ga PPM |
|---------------|---------------|-------|--------|-------|--------|--------|--------|--------|--------|-------|--------|-------|--------|
| RW REEF C | | 28 | <20 | <20 | 1 | 1.00 | 0.33 | 0.34 | 0.08 | 0.36 | 23 | 2 | 2 |



BONDAR CLEGG



Geochemical
Lab
Report

CLIENT: BEAU PRE EXPLORATIONS LTD.

PORT: V01-00122.0 (COMPLETE)

DATE RECEIVED: 26-JAN-01

PROJECT: NONE GIVEN

DATE PRINTED: 9-FEB-01

PAGE 10 (4 / 8)

| SAMPLE | ELEMENT | Li | Nb | Sc | Ta | Ti | Zr | S |
|-----------|---------|-----|-----|-----|-----|-------|-----|------|
| NUMBER | UNITS | PPM | PPM | PPM | PPM | PCT | PPM | PCT |
| SW REEF C | | 6 | <1 | <5 | <10 | 0.049 | <1 | 1.97 |

BC

BONDAR CLEGG



Geochemical Lab Report

BEAU PRE EXPLORATIONS LTD.
#108-3930 SHELBOUNE ST.
VICTORIA, B.C.
V8P 5P6

A handwritten signature in black ink, appearing to read 'R. J. ...' followed by a date 'July 1998'.

+ + + +





BONDAR CLEGG



Geochemical Lab Report

REPORT: V01-00122.0 (COMPLETE)

REFERENCE:

CLIENT: BEAU PRE EXPLORATIONS LTD.

SUBMITTED BY: UNKNOWN

PROJECT: NONE GIVEN

DATE RECEIVED: 26-JAN-01

DATE PRINTED: 9-FEB-01

| APPROVED | ORDER | ELEMENT | NUMBER OF ANALYSES | LOWER | | | METHOD |
|----------|-------|------------------------------|--------------------|-----------|-----------------|------------|---------------------|
| | | | | | DETECTION LIMIT | EXTRACTION | |
| 010130 | 1 | Wt (-) Pulp Wt. Minus Fract. | 1 | 9 | | | FIRE ASSAY |
| 010130 | 2 | WT (+) Pulp wt. Plus Fract | 1 | 0.01 g | | | FIRE ASSAY |
| 010130 | 3 | Au (-) Gold. Minus Fraction | 1 | 0.001 OPT | | | FIRE ASSAY |
| 010130 | 4 | Au (+) Gold. Plus Fraction | 1 | 0.01 OPT | | | FIRE ASSAY |
| 010130 | 5 | Au Tot Gold in total sample | 1 | 0.005 OPT | | | FIRE ASSAY |
| 010130 | 6 | Ag-150 Silver Avg-150 mesh. | 1 | 0.02 OPT | | | FIRE ASSAY |
| 010130 | 7 | Ag+150 Silver in +150 mesh. | 1 | 0.1 OPT | | | FIRE ASSAY |
| 010130 | 8 | Ag Tot Ag in total sample. | 1 | 0.05 OPT | | | FIRE ASSAY |
| 010130 | 9 | Ag - ICO1 | 1 | 0.2 PPM | HCL:HN03 (3:1) | | INDUC. COUP. PLASMA |
| 010130 | 10 | Cu Cu - ICO1 | 1 | 1 PPM | HCL:HN03 (3:1) | | INDUC. COUP. PLASMA |
| 010130 | 11 | Pb Pb - ICO1 | 1 | 2 PPM | HCL:HN03 (3:1) | | INDUC. COUP. PLASMA |
| 010130 | 12 | Zn Zn - ICO1 | 1 | 1 PPM | HCL:HN03 (3:1) | | INDUC. COUP. PLASMA |
| 010130 | 13 | Mo Mo - ICO1 | 1 | 1 PPM | HCL:HN03 (3:1) | | INDUC. COUP. PLASMA |
| 010130 | 14 | Ni Ni - ICO1 | 1 | 1 PPM | HCL:HN03 (3:1) | | INDUC. COUP. PLASMA |
| 010130 | 15 | Co Co - ICO1 | 1 | 1 PPM | HCL:HN03 (3:1) | | INDUC. COUP. PLASMA |
| 010130 | 16 | Cd Cd - ICO1 | 1 | 0.2 PPM | HCL:HN03 (3:1) | | INDUC. COUP. PLASMA |
| 010130 | 17 | Bi Bi - ICO1 | 1 | 5 PPM | HCL:HN03 (3:1) | | INDUC. COUP. PLASMA |
| 010130 | 18 | As As - ICO1 | 1 | 5 PPM | HCL:HN03 (3:1) | | INDUC. COUP. PLASMA |
| 010130 | 19 | Sb Sb - ICO1 | 1 | 5 PPM | HCL:HN03 (3:1) | | INDUC. COUP. PLASMA |
| 010130 | 20 | Fe Fe - ICO1 | 1 | 0.01 PCT | HCL:HN03 (3:1) | | INDUC. COUP. PLASMA |
| 010130 | 21 | Mn Mn - ICO1 | 1 | 1 PPM | HCL:HN03 (3:1) | | INDUC. COUP. PLASMA |
| 010130 | 22 | Te Te - ICO1 | 1 | 10 PPM | HCL:HN03 (3:1) | | INDUC. COUP. PLASMA |
| 010130 | 23 | Ba Ba - ICO1 | 1 | 1 PPM | HCL:HN03 (3:1) | | INDUC. COUP. PLASMA |
| 010130 | 24 | Cr Cr - ICO1 | 1 | 1 PPM | HCL:HN03 (3:1) | | INDUC. COUP. PLASMA |
| 010130 | 25 | V V - ICO1 | 1 | 1 PPM | HCL:HN03 (3:1) | | INDUC. COUP. PLASMA |
| 010130 | 26 | Sn Sn - ICO1 | 1 | 20 PPM | HCL:HN03 (3:1) | | INDUC. COUP. PLASMA |
| 010130 | 27 | W W - ICO1 | 1 | 20 PPM | HCL:HN03 (3:1) | | INDUC. COUP. PLASMA |
| 010130 | 28 | La La - ICO1 | 1 | 1 PPM | HCL:HN03 (3:1) | | INDUC. COUP. PLASMA |
| 010130 | 29 | Al Al - ICO1 | 1 | 0.01 PCT | HCL:HN03 (3:1) | | INDUC. COUP. PLASMA |
| 010130 | 30 | Mg Mg - ICO1 | 1 | 0.01 PCT | HCL:HN03 (3:1) | | INDUC. COUP. PLASMA |
| 010130 | 31 | Ca Ca - ICO1 | 1 | 0.01 PCT | HCL:HN03 (3:1) | | INDUC. COUP. PLASMA |
| 010130 | 32 | Na Na - ICO1 | 1 | 0.01 PCT | HCL:HN03 (3:1) | | INDUC. COUP. PLASMA |
| 010130 | 33 | K K - ICO1 | 1 | 0.01 PCT | HCL:HN03 (3:1) | | INDUC. COUP. PLASMA |
| 010130 | 34 | Sr Sr - ICO1 | 1 | 1 PPM | HCL:HN03 (3:1) | | INDUC. COUP. PLASMA |
| 010130 | 35 | Y Y - ICO1 | 1 | 1 PPM | HCL:HN03 (3:1) | | INDUC. COUP. PLASMA |
| 010130 | 36 | Ga Ga - ICO1 | 1 | 2 PPM | HCL:HN03 (3:1) | | INDUC. COUP. PLASMA |
| 010130 | 37 | Li Li - ICO1 | 1 | 1 PPM | HCL:HN03 (3:1) | | INDUC. COUP. PLASMA |

CLIENT: BEAU PRE EXPLORATIONS LTD.

REPORT: V01-00122.0 (COMPLETE)

PROJECT: NONE GIVEN

DATE RECEIVED: 26-JAN-01

DATE PRINTED: 9-FEB-01

PAGE 2A(5 / 8)

| STANDARD
NAME | ELEMENT
UNITS | Wt (-)
g | WT (+)
g | Au (-)
OPT | Au (+)
OPT | Au Tot
OPT | Ag-150
OPT | Ag+150
OPT | Ag Tot
OPT | Ag
PPM | Cu
PPM | Pb
PPM | Zn
PPM |
|--------------------|------------------|-------------|-------------|---------------|---------------|---------------|---------------|---------------|---------------|-----------|-----------|-----------|-----------|
| ANALYTICAL BLANK | | - | - | <0.001 | - | - | <0.05 | - | - | <0.2 | <1 | <2 | <1 |
| Number of Analyses | | - | - | 1 | - | - | 1 | - | - | 1 | 1 | 1 | 1 |
| Mean Value | | - | - | 0.0004 | - | - | 0.025 | - | - | 0.10 | 0.5 | 1.0 | 0.5 |
| Standard Deviation | | - | - | - | - | - | - | - | - | - | - | - | - |
| Accepted Value | | <0.1 | <0.01 | <0.001 | <0.01 | <0.001 | <0.01 | <0.1 | <0.01 | 0.2 | 1 | 2 | 1 |
| OX11 Oxide | | - | - | 0.090 | - | - | 0.71 | - | - | - | - | - | - |
| Number of Analyses | | - | - | 1 | - | - | 1 | - | - | - | - | - | - |
| Mean Value | | - | - | 0.0897 | - | - | 0.712 | - | - | - | - | - | - |
| Standard Deviation | | - | - | - | - | - | - | - | - | - | - | - | - |
| Accepted Value | | - | - | 0.086 | - | - | 0.73 | 0.7 | - | - | - | - | - |
| OX12 Oxide | | - | 31.15 | - | 0.20 | - | - | 0.3 | - | - | - | - | - |
| Number of Analyses | | - | 1 | - | 1 | - | - | 1 | - | - | - | - | - |
| Mean Value | | - | 31.150 | - | 0.203 | - | - | 0.30 | - | - | - | - | - |
| Standard Deviation | | - | - | - | - | - | - | - | - | - | - | - | - |
| Accepted Value | | - | - | 0.192 | - | - | 0.30 | 0.3 | - | - | - | - | - |
| CANMET LKSD-2 | | - | - | - | - | - | - | - | - | 0.3 | 34 | 35 | 172 |
| Number of Analyses | | - | - | - | - | - | - | - | - | 1 | 1 | 1 | 1 |
| Mean Value | | - | - | - | - | - | - | - | - | 0.31 | 34.3 | 35.1 | 171.6 |
| Standard Deviation | | - | - | - | - | - | - | - | - | - | - | - | - |
| Accepted Value | | - | - | - | - | - | - | - | - | 0.8 | 36 | 40 | 200 |

CLIENT: BEAU PRE EXPLORATIONS LTD.

REPORT: V01-00122.0 (COMPLETE)

PROJECT: NONE GIVEN

DATE RECEIVED: 26-JAN-01

DATE PRINTED: 9-FEB-01

PAGE 2B(6 / 8)

| STANDARD
NAME | ELEMENT
UNITS | Mo
PPM | Ni
PPM | Co
PPM | Cd
PPM | Bi
PPM | As
PPM | Sb
PPM | Fe
PCT | Mn
PPM | TE
PPM | Ba
PPM | Cr
PPM |
|--------------------|------------------|-----------|-----------|-----------|-----------|-----------|-----------|-----------|-----------|-----------|-----------|-----------|-----------|
| ANALYTICAL BLANK | | <1 | <1 | <1 | <0.2 | <5 | <5 | <5 | <0.01 | 1 | <10 | <1 | <1 |
| Number of Analyses | | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 |
| Mean Value | | 0.5 | 0.5 | 0.5 | 0.10 | 2.5 | 2.5 | 2.5 | 0.005 | 1.1 | 5.0 | 0.5 | 0.5 |
| Standard Deviation | | - | - | - | - | - | - | - | - | - | - | - | - |
| Accepted Value | | 1 | 1 | 1 | 0.1 | 2 | 5 | 5 | 0.05 | 1 | <1 | <1 | 1 |
| OX11 Oxide | | - | - | - | - | - | - | - | - | - | - | - | - |
| Number of Analyses | | - | - | - | - | - | - | - | - | - | - | - | - |
| Mean Value | | - | - | - | - | - | - | - | - | - | - | - | - |
| Standard Deviation | | - | - | - | - | - | - | - | - | - | - | - | - |
| Accepted Value | | - | - | - | - | - | - | - | - | - | - | - | - |
| OX12 Oxide | | - | - | - | - | - | - | - | - | - | - | - | - |
| Number of Analyses | | - | - | - | - | - | - | - | - | - | - | - | - |
| Mean Value | | - | - | - | - | - | - | - | - | - | - | - | - |
| Standard Deviation | | - | - | - | - | - | - | - | - | - | - | - | - |
| Accepted Value | | - | - | - | - | - | - | - | - | - | - | - | - |
| CANMET LKSD-2 | | 2 | 24 | 17 | 1.0 | <5 | 19 | <5 | 3.84 | 1714 | <10 | 211 | 25 |
| Number of Analyses | | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 |
| Mean Value | | 2.0 | 24.1 | 17.5 | 1.04 | 2.5 | 19.2 | 2.5 | 3.835 | 1714.1 | 5.0 | 210.6 | 25.5 |
| Standard Deviation | | - | - | - | - | - | - | - | - | - | - | - | - |
| Accepted Value | | 2 | 23 | 17 | 0.8 | - | 9 | 1 | 3.50 | 1840 | - | - | 29 |

CLIENT: BEAU PRE EXPLORATIONS LTD.

REPORT: V01-00122.0 (COMPLETE)

PROJECT: NONE GIVEN

DATE RECEIVED: 26-JAN-01

DATE PRINTED: 9-FEB-01

PAGE 2C(7 / 8)

| STANDARD
NAME | ELEMENT
UNITS | V
PPM | Sn
PPM | W
PPM | La
PPM | Al
PCT | Mg
PCT | Ca
PCT | Na
PCT | K
PCT | Sr
PPM | Y
PPM | Ga
PPM |
|--------------------|------------------|----------|-----------|----------|-----------|-----------|-----------|-----------|-----------|----------|-----------|----------|-----------|
| ANALYTICAL BLANK | | <1 | <20 | <20 | <1 | <0.01 | <0.01 | <0.01 | <0.01 | <0.01 | <1 | <1 | <2 |
| Number of Analyses | | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 |
| Mean Value | | 0.5 | 10.0 | 10.0 | 0.5 | 0.005 | 0.005 | 0.005 | 0.005 | 0.005 | 0.5 | 0.5 | 1.0 |
| Standard Deviation | | - | - | - | - | - | - | - | - | - | - | - | - |
| Accepted Value | | 1 | <1 | <1 | <1 | <0.01 | <0.01 | <0.01 | <0.01 | <0.01 | <1 | <1 | <1 |
| OX11 Oxide | | - | - | - | - | - | - | - | - | - | - | - | - |
| Number of Analyses | | - | - | - | - | - | - | - | - | - | - | - | - |
| Mean Value | | - | - | - | - | - | - | - | - | - | - | - | - |
| Standard Deviation | | - | - | - | - | - | - | - | - | - | - | - | - |
| Accepted Value | | - | - | - | - | - | - | - | - | - | - | - | - |
| OX12 Oxide | | - | - | - | - | - | - | - | - | - | - | - | - |
| Number of Analyses | | - | - | - | - | - | - | - | - | - | - | - | - |
| Mean Value | | - | - | - | - | - | - | - | - | - | - | - | - |
| Standard Deviation | | - | - | - | - | - | - | - | - | - | - | - | - |
| Accepted Value | | - | - | - | - | - | - | - | - | - | - | - | - |
| CANMET LKSD-2 | | 42 | <20 | <20 | 54 | 1.72 | 0.67 | 0.67 | 0.03 | 0.25 | 30 | 26 | 4 |
| Number of Analyses | | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 | 1 |
| Mean Value | | 42.1 | 10.0 | 10.0 | 53.5 | 1.716 | 0.672 | 0.669 | 0.035 | 0.251 | 30.5 | 25.8 | 4.3 |
| Standard Deviation | | - | - | - | - | - | - | - | - | - | - | - | - |
| Accepted Value | | 48 | - | - | - | - | - | - | - | - | - | - | - |



BONDAR CLEGG



Geochemical Lab Report

CLIENT: BEAU PRE EXPLORATIONS LTD.

REPORT: V01-00122.0 (COMPLETE)

PROJECT: NONE GIVEN

DATE RECEIVED: 26-JAN-01

DATE PRINTED: 9-FEB-01

PAGE 2D (8 / 8)

| STANDARD
NAME | ELEMENT
UNITS | Li
PPM | Nb
PPM | Sc
PPM | Ta
PPM | Ti
PCT | Zr
PPM | S
PCT |
|--------------------|------------------|-----------|-----------|-----------|-----------|-----------|-----------|----------|
| ANALYTICAL BLANK | | <1 | <1 | <5 | <10 | <0.010 | <1 | <0.01 |
| Number of Analyses | | 1 | 1 | 1 | 1 | 1 | 1 | 1 |
| Mean Value | | 0.5 | 0.5 | 2.5 | 5.0 | 0.0050 | 0.5 | 0.005 |
| Standard Deviation | | - | - | - | - | - | - | - |
| Accepted Value | | <1 | <1 | <1 | <1 | <0.001 | <1 | <0.01 |
| OX11 Oxide | | - | - | - | - | - | - | - |
| Number of Analyses | | - | - | - | - | - | - | - |
| Mean Value | | - | - | - | - | - | - | - |
| Standard Deviation | | - | - | - | - | - | - | - |
| Accepted Value | | - | - | - | - | - | - | - |
| OX12 Oxide | | - | - | - | - | - | - | - |
| Number of Analyses | | - | - | - | - | - | - | - |
| Mean Value | | - | - | - | - | - | - | - |
| Standard Deviation | | - | - | - | - | - | - | - |
| Accepted Value | | - | - | - | - | - | - | - |
| CANMET LKSD-2 | | 16 | 4 | 6 | <10 | 0.076 | 2 | 0.17 |
| Number of Analyses | | 1 | 1 | 1 | 1 | 1 | 1 | 1 |
| Mean Value | | 15.7 | 3.8 | 6.0 | 5.0 | 0.0757 | 2.2 | 0.168 |
| Standard Deviation | | - | - | - | - | - | - | - |
| Accepted Value | | - | - | - | - | - | - | - |



BONDAR CLEGG



VANCOUVER BRANCH

Geochemical
Lab
Report

GANG C. KOMA

REPORT: V01-00122.0 (COMPLETE)

REFERENCE:

CLIENT: BEAU PRE EXPLORATIONS LTD.

SUBMITTED BY: UNKNOWN

PROJECT: NONE GIVEN

DATE RECEIVED: 26-JAN-01

DATE PRINTED: 9-FEB-01

| APPROVED | ORDER | ELEMENT | DATE | NUMBER OF | LOWER | EXTRACTION | METHOD |
|----------|-------|---------|-----------|-----------|-----------------|----------------|---------------------|
| | | | | ANALYSES | DETECTION LIMIT | | |
| 010130 | 38 | Nb | Nb - IC01 | 1 | 1 PPM | HCL:HNO3 (3:1) | INDUC. COUP. PLASMA |
| 010130 | 39 | Sc | Sc - IC01 | 1 | 5 PPM | HCL:HNO3 (3:1) | INDUC. COUP. PLASMA |
| 010130 | 40 | Ta | Ta - IC01 | 1 | 10 PPM | HCL:HNO3 (3:1) | INDUC. COUP. PLASMA |
| 010130 | 41 | Ti | Ti - IC01 | 1 | 0.010 PCT | HCL:HNO3 (3:1) | INDUC. COUP. PLASMA |
| 010130 | 42 | Zr | Zr - IC01 | 1 | 1 PPM | HCL:HNO3 (3:1) | INDUC. COUP. PLASMA |
| 010130 | 43 | S | S - IC01 | 1 | 0.01 PCT | HCL:HNO3 (3:1) | INDUC. COUP. PLASMA |

| SAMPLE TYPES | NUMBER | SIZE FRACTIONS | NUMBER | SAMPLE PREPARATIONS | NUMBER |
|--------------|--------|----------------|--------|---------------------|--------|
| R ROCK | 1 | W +150/-150 | 1 | CRUSH ONLY | 1 |



REMARKS: High std for As is due to carry over. LON

REPORT COPIES TO: #108-3930 SHELBONUE ST.

INVOICE TO: #108-3930 SHELBONUE ST.

This report must not be reproduced except in full. The data presented in this report is specific to those samples identified under "Sample Number" and is applicable only to the samples as received expressed on a dry basis unless otherwise indicated



BONDAR CLEGG



VANCOUVER BRANCH

Geochemical
Lab
Report

CLIENT: BEAU PRE EXPLORATIONS LTD.

REPORT: V01-00122.0 (COMPLETE)

PROJECT: NONE GIVEN

DATE RECEIVED: 26-JAN-01

DATE PRINTED: 9-FEB-01

PAGE 1A(1 / 8)

| SAMPLE | ELEMENT | WT (-) | WT (+) | Au (-) | Au (+) | Au Tot | Ag-150 | Ag+150 | Ag Tot | Ag | Cu | Pb | Zn |
|-----------|---------|--------|--------|--------|---------|--------|--------|--------|--------|------|-----|-----|-----|
| NUMBER | UNITS | g | g | OPT | OPT | OPT | OPT | OPT | OPT | PPM | PPM | PPM | PPM |
| RW REEF C | | 1038.0 | 44.11 | 27.110 | 1070.54 | 69.644 | 2.13 | 87.1 | 5.60 | 70.0 | 66 | 717 | 24 |

Bondar Clegg Canada Limited

130 Pemberton Avenue, North Vancouver, BC, V7P 2R5, Canada

Tel: (604) 985-0681, Fax: (604) 985-1071



BONDAR CLEGG



VANCOUVER BRANCH

Geochemical
Lab
Report

CLIENT: BEAU PRE EXPLORATIONS LTD.

PROJECT: NONE GIVEN

REPORT: V01-00122.0 (COMPLETE)

DATE RECEIVED: 26-JAN-01

DATE PRINTED: 9-FEB-01

PAGE "B(2 / 8)

| SAMPLE | ELEMENT | Mo | Ni | Co | Cd | Bi | As | Sb | Fe | Mn | Te | Ba | Cr |
|-----------|---------|-----|-----|-----|-------|-----|--------|-----|------|-----|-----|-----|-----|
| NUMBER | UNITS | PPM | PPM | PPM | PPM | PPM | PPM | PPM | PCT | PPM | PPM | PPM | PPM |
| RW REEF C | | 7 | 35 | 14 | 105.4 | <5 | >10000 | 15 | 4.39 | 110 | <10 | 61 | 177 |



BONDAR CLEGG

Geochemical
Lab
Report

CLIENT: BEAU PRE EXPLORATIONS LTD.

PROJECT: NONE GIVEN

REPORT: V01-00122.0 (COMPLETE)

DATE RECEIVED: 26-JAN-01

DATE PRINTED: 9-FEB-01

PAGE 10(3 / 8)

| SAMPLE
NUMBER | ELEMENT
UNITS | V
PPM | Sn
PPM | W
PPM | La
PPM | Al
PCT | Mg
PCT | Ca
PCT | Na
PCT | K
PCT | Sr
PPM | Y
PPM | Ga
PPM |
|------------------|------------------|----------|-----------|----------|-----------|-----------|-----------|-----------|-----------|----------|-----------|----------|-----------|
| RW REEF C | | 28 | <20 | <20 | 1 | 1.00 | 0.33 | 0.34 | 0.08 | 0.36 | 23 | 2 | 2 |



BONDAR CLEGG



Geochemical Lab Report

CLIENT: BEAU PRE EXPLORATIONS LTD.

PROJECT: NONE GIVEN

REPORT: V01-00122.0 (COMPLETE)

DATE RECEIVED: 26-JAN-01

DATE PRINTED: 9-FEB-01

PAGE 1D (4 / 8)

| SAMPLE
NUMBER | ELEMENT
UNITS | Li
PPM | Nb
PPM | Sc
PPM | Ta
PPM | Ti
PCT | Zr
PPM | S
PCT |
|------------------|------------------|-----------|-----------|-----------|-----------|-----------|-----------|----------|
| RW REEF C | | 6 | <1 | <5 | <10 | 0.049 | <1 | 1.97 |



BONDAR CLEGG



Geochemical
Lab
Report

A4)

BEAU PRE EXPLORATIONS LTD.
#108-3930 SHELBURNE ST.
VICTORIA, B.C.
V8P 5P6

+ + + +

ZP



BONDAR CLEGG



Geochemical Lab Report

REPORT: V00-02240.0 (COMPLETE)

REFERENCE:

CLIENT: BEAU PRE EXPLORATIONS LTD.

SUBMITTED BY: UNKNOWN

PROJECT: NONE GIVEN

DATE RECEIVED: 07-DEC-00

DATE PRINTED: 13-DEC-00

| APPROVED | DATE | ELEMENT | NUMBER OF ANALYSES | LOWER | | METHOD |
|--------------|------|------------------------------|--------------------|-----------------|---------------------|-------------------|
| | | | | DETECTION LIMIT | EXTRACTION | |
| 001213 | 1 | Wt (-) Pulp Wt. Minus Fract. | 1 | 9 | | FIRE ASSAY |
| 001213 | 2 | WT (+) Pulp wt. Plus Fract | 1 | 0.01 g | | FIRE ASSAY |
| 001213 | 3 | Au (-) Gold. Minus Fraction | 1 | 0.001 OPT | | FIRE ASSAY |
| 001213 | 4 | Au (+) Gold. Plus Fraction | 1 | 0.01 OPT | | FIRE ASSAY |
| 001213 | 5 | Au Tot Gold in total sample | 1 | 0.005 OPT | | FIRE ASSAY |
| 001213 | 6 | Ag-150 Silver Avg-150 mesh. | 1 | 0.02 OPT | | FIRE ASSAY |
| 001213 | 7 | Ag+150 Silver in +150 mesh. | 1 | 0.1 OPT | | FIRE ASSAY |
| 001213 | 8 | Ag Tot Ag in total sample. | 1 | 0.02 OPT | | FIRE ASSAY |
| 001213 | 9 | As Arsenic | 1 | 5 PPM | HCL:HNO3 (3:1) | ATOMIC ABSORPTION |
| SAMPLE TYPES | | NUMBER | SIZE FRACTIONS | NUMBER | SAMPLE PREPARATIONS | NUMBER |
| R ROCK | | 1 | 2 -150 | 1 | CRUSH/SPLIT & PULV. | 1 |
| | | | | | METALLICS SCREENING | 1 |

REPORT COPIES TO: #108-3930 SHELBURNE ST.

INVOICE TO: #108-3930 SHELBURNE ST.

This report must not be reproduced except in full. The data presented in this report is specific to those samples identified under "Sample Number" and is applicable only to the samples as received expressed on a dry basis unless otherwise indicated

Bondar Clegg Canada Limited

130 Pemberton Avenue, North Vancouver, BC, V7P 2R5, Canada

Tel: (604) 985-0681, Fax: (604) 985-1071

BC

BONDAR CLEGG



Geochemical Lab Report

CLIENT: BEAU PRE EXPLORATIONS LTD.

REPORT: V00-02240.0 (COMPLETE)

DATE RECEIVED: 07-DEC-00

PROJECT: NONE GIVEN

DATE PRINTED: 13-DEC-00

PAGE 1 OF 3

| SAMPLE
NUMBER | ELEMENT
UNITS | Wt (-)
g | WT (+)
g | Au (-)
OPT | Au (+)
OPT | Au Tot
OPT | Ag-150
OPT | Ag+150
OPT | Ag Tot
OPT | As
PPM |
|------------------|------------------|-------------|-------------|---------------|---------------|---------------|---------------|---------------|---------------|-----------|
| R2 22665 | | 183.9 | 4.68 | <0.001 | <0.01 | <0.005 | <0.02 | <0.1 | <0.02 | <5 |

CLIENT: BEAU PRE EXPLORATIONS LTD.

REPORT: V00-02240.0 (COMPLETE)

PROJECT: NONE GIVEN

DATE RECEIVED: 07-DEC-00

DATE PRINTED: 13-DEC-00

PAGE 2 OF 3

| STANDARD
NAME | ELEMENT
UNITS | WT (-)
g | WT (+)
g | Au (-)
OPT | Au (+)
OPT | AU Tot
OPT | Ag-150
OPT | Ag+150
OPT | Ag Tot
OPT | As
PPM |
|--------------------|------------------|-------------|-------------|---------------|---------------|---------------|---------------|---------------|---------------|-----------|
| CANMET STSD-4 | | - | - | - | - | - | - | - | - | 9 |
| Number of Analyses | | - | - | - | - | - | - | - | - | 1 |
| Mean Value | | - | - | - | - | - | - | - | - | 8.8 |
| Standard Deviation | | - | - | - | - | - | - | - | - | - |
| Accepted Value | | - | - | - | - | - | - | - | - | 11 |
| ANALYTICAL BLANK | | - | - | <0.001 | - | - | <0.02 | - | - | <5 |
| Number of Analyses | | - | - | 1 | - | - | 1 | - | - | 1 |
| Mean Value | | - | - | 0.0004 | - | - | 0.010 | - | - | 2.5 |
| Standard Deviation | | - | - | - | - | - | - | - | - | - |
| Accepted Value | | <0.1 | <0.01 | <0.001 | <0.01 | <0.001 | <0.01 | <0.1 | <0.01 | <1 |
| OX11 Oxide | | - | - | 0.090 | - | - | 0.67 | - | - | - |
| Number of Analyses | | - | - | 1 | - | - | 1 | - | - | - |
| Mean Value | | - | - | 0.0904 | - | - | 0.671 | - | - | - |
| Standard Deviation | | - | - | - | - | - | - | - | - | - |
| Accepted Value | | - | - | 0.086 | - | - | 0.73 | 0.7 | - | - |
| OX12 Oxide | | - | 31.13 | - | 0.20 | - | - | - | - | - |
| Number of Analyses | | - | 1 | - | 1 | - | - | - | - | - |
| Mean Value | | - | 31.130 | - | 0.195 | - | - | - | - | - |
| Standard Deviation | | - | - | - | - | - | - | - | - | - |
| Accepted Value | | - | - | 0.192 | - | - | 0.30 | 0.3 | - | - |



BONDAR CLEGG

Geochemical
Lab
ReportCLIENT: BEAU PRE EXPLORATIONS LTD.
REPORT: V00-02240.0 (COMPLETE)

DATE RECEIVED: 07-DEC-00

PROJECT: NONE GIVEN

DATE PRINTED: 13-DEC-00

PAGE 3 OF 3

| SAMPLE
NUMBER | ELEMENT
UNITS | WT (-)
g | WT (+)
g | AU (-)
OPT | AU (+)
OPT | AU Tot
OPT | Ag-150
OPT | Ag+150
OPT | Ag Tot
OPT | As
PPM |
|------------------|------------------|-------------|-------------|---------------|---------------|---------------|---------------|---------------|---------------|-----------|
| 22665 | | 183.9 | 4.68 | <0.001 | <0.01 | <0.005 | <0.02 | <0.1 | <0.02 | <5 |
| Duplicate | | | | | | | | | | |