

RECEIVED
DEC 31 2002
Gold Commissioner's Office
VANCOUVER, B.C.

ASSESSMENT REPORT

ON THE

BT 1-6 & 8 CLAIMS

CARIBOO MINING DIVISION BRITISH COLUMBIA

LAT 54° 03' N LONG 121° 36' W

N.T.S. 93 I 4

FOR

26BT RESOURCE DEVELOPMENT CO. LTD.

BY

S. JAIN, P. GEOPH (ALBERTA), P. GEO. (B.C.)

&

W. L. KELSCH, P. GEOPH (ALBERTA)

**GEOLOGICAL SURVEY BRANCH
ASSESSMENT REPORT**

27,021

December 20, 2002

Calgary, Alberta

SUDHIR JAIN received M.Tech. in Exploration Geophysics from Indian Institute of Technology and Ph.D. in Geophysics from University of Liverpool. After working for twelve years for Mobil and sundry service companies in U.K., Libya, U.S.A., and Canada, Dr. Jain set up Commonwealth Geophysical, a service company for oil and mineral exploration in 1976. He developed innovative interpretation techniques for geophysical data which quickly became industry standards. He published over 40 papers and was honoured by European and Canadian professional societies.

Since 1974, Dr. Jain has explored for numerous companies in Canada and overseas as well as in Madagascar and Southeastern Alberta on his own account. He is also associated with ore exploration in British Columbia and diamond exploration in Saskatchewan. He is a registered Geoscientist in British Columbia, a member of Association of Professional Engineers, Geologists and Geophysicists of Alberta, and honorary member of Canadian Society of Exploration Geophysicists.

LORNE KELSCH graduated with B.Sc. from University of Manitoba in 1952. After working on seismic data acquisition, processing and interpretation for 22 years with Petty Ray Geophysical, Mr. Kelsch moved to PanCanadian where he worked in various capacities including Chief Geophysicist till his retirement in 1995.

Mr. Kelsch is a professional member of Association of Professional Engineers, Geologists and Geophysicists of Alberta, Canadian Society of Exploration Geophysicists.

CONTENTS

	PAGE
INTRODUCTION	
Claim Data	1
Location & Access	1
History	1-2
Geology	3
Geophysics	
Data Acquisition in 1993	3
Data Acquisition in 1997	4
Interpretation of E-M Data	4
DRILLING AND CORE ANALYSIS	4-5
INTEGRATION OF GEOLOGY AND GEOPHYSICS	5
Silt Samples	5
Rock Samples	6
Ground Geophysical Survey	6
Composite Sample Separation and Analyses of Ilmenite and Magnetite	6-7
CURRENT WORK - GOLD PROSPECT	7-9
CONCLUSIONS AND FUTURE WORK	9
References	10

	PAGE
Figure 1 - Area of 26BT claims area of aeromagnetic and EM survey in 1993 is shaded.	In back pocket
Figure 2 - Geological map of Bearpaw Ridge	In back pocket
Figure 3 - Location of holes drilled	In back pocket
Figure 4 - Map showing gold content in ppb from surance samples	In back pocket
Appendix 1 - Details of drilling in 1994, 1995, 1996 and 2000	11
Appendix 2 - The assay of samples collected in October 2001	12-22
Appendix 2A- The assay of 6 rock samples from the area of Appendix 2	23-24
Appendix 3 - Gold assays of chip samples from 95-2 and 95-3	25-26
Appendix 4A- Assays of 5' sections in hole 95-2	27
Appendix 4B- Assays of gold rich silt sample 5105 after magnetic separation	28
Appendix 4C- Assays of 1' and 5' core sections in hole 95-3	29-31
Appendix 5 - Assays of rock and wilt samples scatterd over th claim area	32-37
Appendix 6 - Assays of 563 soil samples collected in August and October 2002	38-57
STATEMENT OF COSTS (October 03, 2001 to October 02, 2002)	58

INTRODUCTION

Claim Data

The B.T. Properties are presently held in the name of 26BT Resource Development Co. Ltd. They were originally staked by Brendan A. Gordon on behalf of Malcolm T. MacDonald, one of the principals of the Company.

<u>Claim Name</u>	<u>Tenure Number</u>	<u>Anniversary Date</u>
BT 1-4	313837-313840	October 8, 1993
BT 5,6	313845-313846	October 8, 1993

These were then sold to the company.

BT 7, 8, 9, 10 and 11 were acquired on behalf of the company in 1993. Details are as follows:

BT 8-10	323096-323098	December 21, 1994
BT 7,11	323202-323203	December 29, 1994

BT 12, 13, 14, 15, 16, 17, 18, 19 and 20 were acquired on behalf of the company by Brendan A. Gordon in June 1996. The details are as follows:

BT 12-17	346620-346625	June 09, 1996
BT 18	346941	June 10, 1996
BT 19	346626	June 10, 1996

This report covers claims 1-6 and 8 only. Claims 7 and 9-20 were relinquished in the year 2000.

Location & Access

The property lies north of the Fraser River and south of the West Torphy River. The centre of the claims is about 6 kilometres N.N.E. of Sinclair Mills (Figure 1). Access to the claims is by old logging roads. The claims lie between the elevation of 700 meters and 1690 meters in generally rugged terrain. Devil's club and windfall trees make the claims difficult to traverse.

History

Two of the principals of the company entered the area north and east of MacGregor in 1989. This was based on projections of the trends seen in the configuration of the North American Continental mass as demonstrated by Government gravity and magnetic maps. Later, while studying reports and maps in the Provincial offices in Prince George, the magnetic feature shown

on Aeromagnetic Map 1536 G of the Geophysics Division of Mines and Technical Surveys was noted. Subsequent sampling along creeks crossing the old logging road north of Sinclair Mills yielded unusually high amounts of magnetite. The decision to stake the area at the north west end of Bearpaw Ridge was then made and carried out in 1992. An aeromagnetic survey was flown, processed and interpreted in 1993. As a result of this survey, additional areas surrounding the claims were staked. 9 holes were drilled to the depth of 100' on the claims in October 1994. The chemical analysis from the cores showed that Fe_2O_3 content averaged between 10 - 20% in the holes and reached up to 35% in some zones. The magnetic separation in 20 samples from two of the holes showed that in samples with high Fe_2O_3 content (greater than 10%), magnetite is more than 75% of total Fe_2O_3 percentage.

Three holes were drilled to the depths of 300' in June 1995. Two of the holes confirmed the presence of magnetite in a variable amount to at least 300'. The third hole was mislocated and missed the anomaly. This hole does not appear to have any commercial significance.

Three holes were drilled in July 1996, two to the depth of 300' and one to 500'. One hole confirmed magnetic concentration while the other two were discouraging. Detailed surface geology was undertaken in 1997 together with mineral and chemical analysis of 60 stream samples and 109 chip samples. The report of professional geologist is included as Appendix 7 in Assessment Report Number 25280.

In the summer of 1998, ground magnetic and VLF-EM data was collected along eleven cut lines and four roads. 25 silt samples and 81 rock samples were also collected by E. R. Kruckowski, P. Geol. and his crew. His report is included as Appendix 2 in Assessment Report Number 25664. Ground geophysical data results are discussed in a later section (Integration of Geology and Geophysics).

In the summer of 1999, ground magnetic data was collected along three extended and two new lines. 63 rock samples and magnetic data at 25' intervals were collected by E.R. Kruckowski, P. Geol. and his crew. Two gravel samples were also collected for detailed analysis. Five cores from previous holes (94-4, 94-6, 95-2, 96-1, and 96-3) were analyzed in detail in 3.3 m (10') sections by Overburden Drilling Management for mineralogical content. Core for 94-4 was analyzed by MD Technologies of Perth, Australia for metallurgical analysis in July to October 1999.

In September 2000 two 92 m deep holes were drilled from the same location (surface sample R224, report no. 26336), one vertical and the other at 45° inclination. The cores were analyzed and selected samples were chemically analyzed Appendix 1 and 2, report no. 26336. The analysis of cores was inconsistent with surface geology and we suspect that the hole was mislocated. Its true location is not known. In 2001 gold was encountered in some silts samples and the focus of exploration shifted to gold from Titanium. Details of this work are described under current work - gold prospect.

Geology

Following summary of known geology of Bearpaw ridge closely follows the report by Pell (1994). The area is mapped as Silurian volcanoclastics, felsic and intermediate tuffs, agglomerates of Nonda formation over the ridge, foliated hornblende gneiss on the western slope and coarse grained massive pink syenites in the southwest (Figure 2). Pell notes sodalite syenite outcrop and two flanking syenite sills in southeast portion of the claim area which intrude the volcanoclastics whose southeastern extent is not defined. These volcanoclastics "largely comprise clinopyroxene crystal tuffs, calcareous tuffs and minor basaltic flows. Flow rocks contain clinopyroxene phenocrysts and altered phenocrysts (now chlorite) in a ground mass of opaque oxides, plagioclase and clinopyroxene microphenocrysts and chlorite". These may be classified as alkali basalts. Folded and foliated dioritic orthogneiss vary from a banded gneiss containing 5 - 10% magnetite-ilmenite to a mafic gneiss with 15 - 20% magnetite-ilmenite. Chemical analyses indicates Fe_2O_3 content of 6.9 and 14.5% in two volcanic samples and 1.5, 7 and 11.2% in three samples from mafic gneiss. Corresponding TiO_2 content is .59 and 2.06% in volcanics and .27, .80 and 2.01% in mafic gneisses.

Kelsch in an appendix to Kelsch and Jain (1994) reported that the accessible part of the terrain is generally covered by a thin layer of soil. The vegetation is thick. Devil's club and mosquitoes are plentiful and they make the work quite difficult. In spite of these problems, he obtained several surface samples. The majority of these samples were from glacial erratics which had not moved very far from their original location. The magnetic susceptibility of these samples ranged from .001 to .250 S.I. units. Two of the samples were analyzed chemically by Terramin Research Labs Ltd. The analysis showed 22 and 25% Iron Oxide and 4.34 and 5% Titanium Oxide in these samples. These figures support more work on the prospect to define concentrations of magnetite and ilmenite which may have economic interest.

The magnetic data acquired by 26BT strongly suggest a magnetite rich intrusive of elliptical shape on the ridge. This is confirmed by the mineralogical analysis of samples from fifteen holes drilled so far which contain crystalline gabbro with high mafic content. The gabbro is quite heterogeneous laterally as well as vertically. Pell (1994) does not mention this intrusive. Incidentally, the sodalite body mapped by Pell was not encountered in hole 95-3.

Geophysics

Data Acquisition in 1993

26BT engaged Geonex Aerodat to conduct an aeromagnetic and electromagnetic survey over a 12 km X 13 km area including the company's claims. The data were acquired in February, 1993 by a helicopter with mean terrain clearance of 100 m for helicopter and 70 m for sensing equipment. The survey comprises 321 line kilometres, with east-west traverse lines spaced 500 m apart and two north-south tie lines. In addition to the total field map with variable contour interval, Geonex also supplied maps for vertical gradient of the magnetic field and VLF-EM total field. The VLF-EM map is relatively quiet and indicates general absence of sulphide ores in the area. The vertical gradient measurements did not provide meaningful data probably because magnetic anomalies were very strong and very sharp. The details of acquisition and preliminary processing are contained in the report submitted by Geonex and included in Kelsch, and Jain (1993). Final processing and interpretation are described by Jain and Kelsch (1997) in Assessment Report Number 25280.

Data Acquisition in 1997

26BT engaged Dighem, A Division of CGG Canada Ltd. to conduct an aeromagnetic and multi-coil, multi-frequency electromagnetic survey over an approximately 62 sq km area. Total coverage amounted to 361 km including tie-lines. The survey was flown on February 8 and February 9, 1997. Dighem processed the data in their Mississauga, Ontario facility and final maps and their report was received by 26BT on April 8, 1997. For technical details of the Dighem report see Assessment Report Number 25034.

Interpretation of E-M Data

This is included in Assessment Report Number 25543 (D.R. Stevenson, P.Geo. electromagnetic data), Assessment Report Number 25664 (Appendix 2) and Assessment Report Number 25034 (Dighem maps).

DRILLING AND CORE ANALYSIS

9 holes were drilled to a depth of 30.46 m (100 ft) in October 1994, 3 holes to the depth of 91.38 m (300 ft) in June 1995 and three holes, two to the depth of 91.38 m (300 ft) and one to 152.29 m (500 ft) in July 1996. All holes were cored in hard rock. Location of the holes is shown in Figure 3. Core diameter was 43 mm (1 ¾"). Hole 7 did not hit the hard rock till it reached the bottom. Susceptibility was measured at 1 ft intervals on the cores as an indicator of the magnetite content. Two boulder specimens collected in 1994 were analyzed. The holes were drilled to determine the source of magnetic anomaly and not for details of local geology. No obvious metals have been noted in the cores. Appendix 1 gives details of the drilling logistics. Core logs are given in Assessment Report Number 25034.

140 samples were selected from fourteen cores to include a wide variety of susceptibility and core type (grain-size, colour, rock type) and two from boulders picked up on the site. Magnetic susceptibility of the samples was measured several times at different locations on the sample and the average recorded.

The samples were chemically analyzed by Terramin Research Labs of Calgary in December, 1994, August, 1995 and October, 1996. The results of their analyses, measured susceptibility and rock type are given in Assessment Report Number 25664.

Cores from five holes, 94-4, 94 6, 95-2, 96-1 and 96-3 were cut in two halves along the diameter. One part was sent to Stu Averill, Overburden Drilling Management Limited, Napean, Ontario. His reports and analyses conducted by them are included in Assessment Report Number 26044. Overall results of this study are generally negative. The summary of Stu Averill's work is as follows:

1. The magnetite in the gabbro contains approximately 10% of its weight in TiO₂ in intercrystalline form. The titaniferous magnetite is of little commercial value.

2. There is no rutile contained in these cores.
3. Ilmenite content ranges from 2.5% to 5% in all holes except 96-4 where it is 10%. 94-4 also contained 2.5% P_2O_5 . However, apatite contained in the core is very fine-grained and may be deleterious to Ilmenite instead of being a by-product. As a result of this analysis, core from 94-4 was sent to MD Technologies in Perth, Australia for metallurgical analysis and review of commerciality of the core. Results from their analysis show that recoverable ilmenite is only 3.2% because substantial proportion of TiO_2 is contained in Pyroxenes as well as in magnetite and that calcium and phosphorus content makes it unsuitable for chloride feed stock but acceptable as sulphate feed stock. Two surface samples from northern part of the ridge had recoverable ilmenite exceeding 10%.

INTEGRATION OF GEOLOGY AND GEOPHYSICS

The geological study conducted in the summer of 1997, 1998 and 1999 by Ed Kruchkowski (see Assessment Report Numbers 25280, 25664 and 26044) provided encouraging results from silt and rock samples. Analyses of these samples generally supported the magnetic data interpretation and drill hole results of previous years. General conclusions from magnetic separation and petrographic studies are:

1. Recoverable magnetite is expected to be 60 - 75% of Fe_2O_3 content of the rock. However, this magnetite is of little commercial interest due to its TiO_2 content.
2. Recoverable ilmenite is expected to be about the same percentage as TiO_2 since pyroxenes and magnetite also contain TiO_2 .
3. Rutile is absent in all five holes analyzed in detail.
4. Apatite is present along the rims of zones with concentrated ilmenite. This apatite is very fine-grained, widely dispersed and probably not commercial.

Silt Samples

86 silt samples were collected in 1997 and 1998 from the stream beds. The chemical analyses showed Fe_2O_3 and TiO_2 content ranges of 5 - 36% and 0.5 - 14% respectively. Iron and titanium contents increased in tandem, TiO_2 being 20 - 40% of Fe_2O_3 . Generally the percentage was at the higher end of the spectrum when the Fe_2O_3 content was higher.

Higher concentrations were noted in streams which flowed through highly magnetic areas than in streams which bypassed such areas. The ground magnetic survey shows that many streams have moved since concentrating magnetite along several kilometres of their lengths. The data indicates the width of concentrated zones ranges from 100 - 200 m. It should be noted that string anomalies are also caused by sources other than streams.

Rock Samples

Rock samples were collected from accessible outcrops in 1997, 1998 and 1999. Chemical analyses of these samples showed that generally TiO_2 is 15 - 35% of Fe_2O_3 , its proportion increases when Fe_2O_3 concentration is high.

The chemical analysis done in 1997 did not include P_2O_5 and V_2O_5 . The analysis for these samples was repeated by Loring Lab in 1999 in Assessment Report Number 26044. This analysis indicates that ilmenite enrichment noted in 94-4 probably extends eastward and may be better than in 94-4. P_2O_5 content seems to be higher along the rims of high ilmenite zones. There is indication of local concentration of V_2O_5 but not to economic levels on its own account.

Ground Geophysical Survey

In June 1998 and 1999, total magnetic field data were collected along slashed lines and four roads. Station spacing was 25 m and line spacing averaged 1 km. The meter, ENVI MAG/VLF, S/N 9602230, was manufactured by and rented from Scintrex. This work is reported in Assessment Report No. 26044. To summarise, manually contoured map of magnetic field shows very strong (2000 -6000 nT) string like anomalies. When these strings follow the dips on topographic map, they indicate magnetite concentration in existing or old streams. When string like anomalies follow the trend of the topographic strikes, they may be due to the outcropping gabbro.

Composite Sample Separation and Analyses of Ilmenite and Magnetite

The crushed core for hole 94-4 was shipped to MD Mineral Technologies in Australia to determine the recoverable grade of ilmenite, magnetite and apatite, composition of ilmenite and magnetite and grain size of ilmenite and magnetite. The report of this analysis (Assessment Report Number 26336) can be summarised as follows:

1. Recoverable percentage of ilmenite totals only 2.9%. This could increase to almost 4.0% on optimum crushing.
2. Ilmenite is suitable for sulphate feedstock.
3. Magnetite contains approximately 15% TiO_2 .
4. Apatite, if any, is not recoverable.

These findings show that the hole itself is not commercial but the areas of higher TiO_2 content could be potentially commercial. Therefore, two crushed rock sample residuals from geochemical analysis for samples R65 and R222 located on the northwest slope of the ridge were sent to MD Minerals for similar analysis. The geochemical analysis had shown that TiO_2

content in these samples was approximately 10%. Unfortunately, fines (-45 micrometer) were 65.2% in R65 and 42% in R222. Even with this unfavourable ratio, the recoverable ilmenite was respectively 2.6% and 8.3% of the whole sample. This translates into maximum of 7.5% and 12.7% respectively. In R222, all of TiO₂ appears to be in ilmenite and magnetite and none in pyroxenes. Recovery of more than 10% ilmenite is probable in an optimally ground sample R222.

CURRENT WORK - GOLD PROSPECT

In April 2001, 15 silt samples scattered over the area of the claims were sent to Loring Labs of Calgary for PGM analysis to review the prospects of gold, palladium and platinum. None of the samples had measurable platinum or palladium. However, two silt samples had gold content of 25 ppb and 1500 ppb. These samples are located on eastern side of the ridge, near an offshoot of the Tintina Regional fault and on the probable edge of the gabbro-rich intrusive. Seven rock samples were also analyzed for gold, copper, lead and zinc but they did not contain any of these elements in appreciable quantity.

Another 30 silt samples and one rock sample were analyzed for PGM elements and 32 element analysis in August 2001. The gold content in 30 samples was as follows:

Gold, ppb	Number of Samples
100 - 815	9
25 - 83	6
08 - 23	6
below 5	9

The only rock sample analyzed tested gold at 7 ppb. The gold values clustered around two good samples tested in the spring. 32 element analysis of these 30 silt samples and 7 rock samples confirmed that there was no other element of economic interest in appreciable quantity. These assays were included in Appendix 3 with the year 2001 report no. 26723.

In early October 2001, 26 stream silt, 14 rock and 166 soil (zone B) samples were collected in the general area of two good silt samples reported last year. The assay of these samples resulted in measurable gold in 8 rock, 4 silt and 37 soil samples. PGM and ICP analyses of these samples are given in Appendix 2. We also analyzed 6 samples from outcrops in this area (Appendix 2A). They showed no gold or other elements of any commercial interest thus setting eastern limit to prospective area.

Three samples from the core of hole 95-2 and one from hole 95-3 were processed by 30 element ICP analysis and also separately for gold. The results are given in Appendix 3. All four samples contained some gold but no other encouraging element. We had analyzed five foot sections from hole 95-2 for magnetite and ilmenite in the year 2000. The remainders of these samples were now analyzed for gold for the depths of 10 to 120 feet (Appendix 4A). Although 8 of 21 segments had some gold, most encouraging was one located within five feet of the highly magnetic gabbro. It assayed 400 ppb of gold. This leads us to the hypothesis that highest

concentration of gold occurs in less magnetic holes. However, silt samples S105 which contained 800 ppb of gold was separated into magnetic and nonmagnetic parts. Nonmagnetic portion, 82.13% of the whole sample, assayed 700 ppb while magnetic portion, 17.82% of the sample, assayed 900 ppb (Appendix 4B). This shows that although gold may be concentrated in less magnetic rocks overlying gabbro, concentration of gold may not be related to magnetite content itself. Hole 96-3 is located southeast of the area outlined as gold prospect. The magnetic susceptibility in the core was very low to 275 feet and slightly higher for 275-300 ft. The core was split diametrically in two parts. One of the parts was further divided into two quarters. One quarter was assayed for gold, palladium, platinum and rhodium in five foot segments from 20-300 feet and the other into one foot segments from 250-284 feet (Appendix 4C). Small gold assays from 5-55 ppb were noted at scattered depth intervals but the values were not high enough to extend the area of commercial interest to the location of this hole.

139 rock and 34 silt samples in our claim area had been analyzed for other elements but not for gold. These samples were assayed for gold, palladium, platinum and rhodium to identify other areas of interest for precious metals on our claim (Appendix 5). Unfortunately, although isolated samples had some gold, no other area of commercial interest was identified.

Based on these results, we collected 563 soil samples (zone B) during August and September of 2002. These samples have been assayed (Appendix 6). Location and gold content (when greater than 5 ppb) is shown in Figure 4. Following table summarises the content of gold in 729 soil samples collected so far.

Gold ppb	Number of samples
0 - 5	503
5 - 9	46
10 - 50	132
51 - 99	17
100 - 500	28
500 or more	3

The gold-bearing samples are grouped into three prospective areas totalling more than three square kilometres. We do not have enough data to be certain whether the areas are connected or not. The areas are open to the west and to the south. The silt sample with a 500 ppb assay is located in this area. In addition, 30 samples out of 563 which were assayed for Palladium had it in varying amounts. One of these measured 140 ppb as well as 394 ppb of gold.

We discussed these results with two geologists, Ed Krutchkowski and Thomas Richards. Both were excited by the results. Thomas suggested that we should confirm these assays by getting another lab to do the analysis on some samples. Accordingly, we sent 10 samples with variable gold assays to Acme Lab in Vancouver for this analysis. Unfortunately, Acme results do not confirm previous results obtained by Loring Lab. This comparison is shown in the following table:

Sample ID	LORING LAB			ACME LAB			Sample Wt (Acme)
	Au	Pt	Pd	Au	Pt	Pd	
95-2 89-90	400			<2	<2	<2	30 gm
0+00N 39+50E	430	<5	<5	<2	2	2	30 gm
0+00N 41+25E	1585	<5	<5	2	7	7	30 gm
0+00N 43+00E	<5	<5	<5	<2	8	4	15 gm
3+00S 28+75E	110	<5	<5	8	<2	8	5 gm
3+00S 34+50E	<5	<5	<5	56	7	<2	5 gm
3+00S 48+75E	7	<5	<5	7	8	12	10 gm
5+00S 36+00E	<5	25	<5	<2	2	2	30 gm
5+00S 39+00E	13	22	<5	<2	<2	8	15 gm
5+00S 40+00E	13	42	<5	3	4	7	15 gm

If Acme are to correct, nine samples have negligible gold and one has higher gold content than Loring found.

CONCLUSIONS AND FUTURE WORK

There are two possible explanations for the conflicting results from two labs. One possibility is that the pots at Loring Labs were contaminated. However, considering the consistency of results from assays at different times, this is not very likely. Other possibility is that gold occurs as very fine particles in samples and is unevenly distributed. Considering that gold content in an excellent assay is less than 15 micrograms, this is quite probable. To resolve the issue, we plan to do a two day survey over our best anomaly. The Geologist will collect large samples from a 10 m grid and these samples will be analyzed from scratch by two different labs. If good assays are confirmed, we will complete the soil grid by filling the empty areas and extending the lines where appropriate. If the results are not confirmed, we will give up on gold and concentrate on Titanium on this claim.

References

Kelsch, W.L., Jain, S., 1993, Assessment report on the BT 1-6 claims: Prince George Mining Division, British Columbia

Kelsch, W.L., Jain, S., 1994, Assessment Report on the BT 1-11 claims: Prince George Mining Division, British Columbia

Pell, J., 1994, *Carbonatites, Nepheline Syenites, Rimberlites and Related rocks in British Columbia: Province of British Columbia, Mineral Resources Division, Bulletin 88, p 14-18*

Jain, S., Kelsch, W.L., 1996, Assessment report number 25034, BT claims 12-19

Jain, S., Kelsch, W.L., 1997, Assessment report number 25164 & 25280, BT claims 1-11

Jain, S., Kelsch, W.L., 1997, Assessment report number 25543, BT claims 12-19

Jain, S., Kelsch, W.L., 1998, Assessment report number 25664, BT claims 1-11

Jain, S., Kelsch, W.L., 1999, *Assessment report number 25770, BT claims 8-10*

Jain, S., Kelsch, W.L., 1999, Assessment report number 26044, BT claims 1-7, BT 11

Jain, S., Kelsch, W.L., 2000, Assessment report number 26336, BT claims 1-6, BT 8

Jain, S., Kelsch, W.K., 2001, Assessment report number 26723, BT claims 1-6, BT 8

APPENDIX 1

Drill hole and core information

Hole diameter	1 ¾" 43 mm	
Inclination	90° and 45° (2000V)	
Azimuth	90° (2000V)	
Minerals noted	no obvious metals noted	
Number of holes	17	
Total hole depth	3500' 1066.8 m	
Total length of core	3181' 969.0 m	
Location of cores	7203 Keewatin Street S.W., Calgary, AB, T2V 2M6	
Collar elevation of holes (estimated from topo map)	94-1	3599' 1097 m
	94-2	3812' 1162 m
	94-3	3924' 1196 m
	94-4	4127' 1258 m
	94-5	3527' 1075 m
	94-6	3665' 1117 m
	94-7	2828' 862 m
	94-8	2749' 838 m
	94-9	2346' 715 m
	95-1	2461' 750 m
	95-2	4550' 1387 m
	95-3	5321' 1622 m
	96-1	2526' 770 m
	96-2	5269' 1606 m
	96-3	5174' 1577 m
	2000-I	4600' 1402 m
	2000-V	4600' 1402 m



Loring Laboratories Ltd.

629 Beaverdam Road N.E.,
Calgary Alberta T2K 4W7
Tel: 274-2777 Fax: 275-0541



TO: 26 BT RESOURCE CO., LTD
Suite 200, 5920 McLeod Trail S.W.,
Calgary, Alberta
T2H 0K2

FILE:44243

DATE:October 26, 2001

Attn: Sudhir Ja -

32 ELEMENT ICP ANALYSIS

Sample No.	Au	Ag	Al	As	B	Ba	Be	Bi	Ca	Cd	Co	Cr	Cu	Fe	K	La	Mg	Mn	Mo	Na	Ni	P	Pb	Sb	Se	Sr	Th	Ti	U	V	W	Zn
	ppb	ppm	%	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	%	%	ppm	%	ppm	ppm	%	ppm	%	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm
1+00N	<5	<0.5	1.55	<1	20	51	<1	<1	0.15	<1	48	27	14	2.83	0.18	16	0.19	421	1	0.03	46	0.24	13	<1	<1	21	52	0.14	<1	58	<1	30
1+25N	<5	<0.5	1.79	<1	17	48	<1	4	0.23	<1	51	17	13	2.67	0.14	9	0.23	332	<1	0.02	56	0.34	15	<1	<1	23	71	0.11	<1	52	<1	31
1+50N	<5	<0.5	1.62	<1	21	57	<1	<1	0.24	<1	65	<1	6	3.93	0.16	12	0.26	215	1	0.03	83	0.21	14	5	<1	26	84	0.15	<1	77	<1	32
1+75N	20	<0.5	1.32	2	19	39	<1	6	0.11	<1	47	32	3	2.82	0.14	<1	0.16	215	<1	0.02	59	0.17	14	<1	<1	26	82	0.13	<1	55	<1	25
2+00N	<5	<0.5	1.60	1	21	53	<1	3	0.13	<1	55	29	1	3.23	0.18	<1	0.17	294	<1	0.02	62	0.18	11	<1	<1	18	107	0.14	<1	70	<1	31
2+25N	10	<0.5	1.39	<1	19	44	<1	4	0.15	<1	34	17	6	1.98	0.14	<1	0.15	142	<1	0.02	43	0.25	14	<1	5	21	49	0.08	<1	37	<1	28
2+50N	<5	<0.5	1.39	<1	20	49	<1	<1	0.44	<1	48	4	6	2.32	0.14	24	0.23	564	<1	0.03	51	0.29	18	<1	3	34	44	0.10	<1	57	<1	37
2+75N	5	<0.5	1.88	<1	14	52	<1	<1	0.10	<1	40	22	9	2.36	0.18	9	0.22	76	2	0.02	54	0.14	13	2	<1	18	50	0.12	<1	60	<1	28
3+00N	5	<0.5	1.37	<1	18	39	<1	<1	0.11	<1	53	32	6	2.76	0.12	12	0.11	677	1	0.02	57	0.14	10	<1	<1	18	7	0.16	<1	81	<1	22
3+25N	10	<0.5	1.51	<1	21	49	<1	2	0.12	<1	59	27	3	3.41	0.13	9	0.11	256	<1	0.02	51	0.25	12	<1	<1	25	50	0.15	<1	91	<1	25
3+50N	<5	<0.5	1.65	<1	17	34	<1	<1	0.22	<1	51	19	3	3.13	0.10	12	0.15	139	<1	0.02	63	0.26	11	<1	<1	16	42	0.11	<1	63	<1	22
3+75N	<5	<0.5	1.76	<1	20	52	<1	<1	0.31	<1	54	40	5	2.64	0.14	14	0.24	500	<1	0.03	47	0.25	12	3	<1	29	55	0.10	<1	50	<1	37
4+00N	5	<0.5	1.17	<1	20	33	<1	<1	0.10	<1	44	37	<1	2.66	0.08	7	0.14	171	<1	0.02	57	0.13	9	<1	<1	12	69	0.12	<1	56	<1	22
0+25S-R	<5	<0.5	1.48	3	22	41	<1	<1	0.11	<1	43	24	10	2.27	0.15	9	0.15	221	<1	0.03	41	0.30	13	<1	<1	16	62	0.15	<1	62	<1	24
STD		1.8	3.89	102	29	27	<1	<1	1.38	2	75	80	65	4.24	0.29	14	1.15	577	4	0.43	199	0.05	106	24	<1	74	<1	0.10	<1	98	<1	129
4+25N	50	<0.5	1.77	<1	20	58	<1	<1	0.33	<1	41	29	9	2.20	0.11	19	0.24	199	<1	0.03	51	0.27	13	<1	<1	21	109	0.07	<1	46	<1	27
4+50N	<5	<0.5	1.81	<1	20	42	<1	3	0.16	<1	51	14	<1	3.10	0.15	9	0.17	206	2	0.02	56	0.22	13	<1	<1	12	132	0.10	<1	55	<1	29
4+75N	5+	<0.5	1.55	<1	21	52	<1	<1	0.18	<1	53	40	1	3.00	0.15	16	0.17	491	<1	0.03	58	0.29	13	2	<1	24	71	0.13	<1	72	<1	26
5+00N	<5	<0.5	1.67	<1	23	36	<1	5	0.14	<1	55	22	5	3.38	0.15	12	0.15	209	<1	0.02	52	0.18	14	<1	<1	15	103	0.14	<1	64	<1	23
5+25N	110	<0.5	1.55	<1	21	78	<1	<1	0.17	<1	54	34	3	3.22	0.09	9	0.14	180	2	0.02	57	0.24	11	<1	<1	24	48	0.15	<1	70	<1	20
5+50N	<5	<0.5	1.67	<1	20	36	<1	1	0.15	<1	52	27	1	3.03	0.12	16	0.14	174	<1	0.02	60	0.21	15	<1	<1	23	91	0.13	<1	77	<1	23
5+75N	<5	<0.5	1.44	<1	20	60	<1	2	0.35	<1	65	19	<1	3.90	0.15	21	0.22	231	<1	0.03	74	0.18	16	<1	<1	25	105	0.13	<1	154	<1	34
6+00N	120	<0.5	2.18	2	22	63	<1	<1	0.89	<1	67	22	<1	4.00	0.06	19	0.26	158	<1	0.04	67	0.35	11	<1	<1	54	54	0.11	<1	122	<1	24
6+25N	<5	<0.5	1.58	1	23	79	<1	2	0.14	<1	65	1	<1	3.88	0.16	12	0.16	295	1	0.02	66	0.18	17	<1	<1	24	88	0.12	<1	79	<1	33
6+50N	<5	<0.5	1.65	<1	28	35	<1	2	0.07	<1	78	24	<1	5.03	0.15	9	0.14	124	1	0.02	80	0.11	16	<1	<1	13	147	0.17	<1	108	<1	21



Loring Laboratories Ltd.

629 Beaverdam Road N.E.,
Calgary Alberta T2K 4W7
Tel: 274-2777 Fax: 275-0541



TO: 26 BT RESOURCE CO., LTD
Suite 200, 5920 McLeod Trail S.W.,
Calgary, Alberta
T2H 0K2

FILE:44243

DATE:October 26, 2001

Attn: Sudhir Jain

APPENDIX 2 (CONTINUED)

32 ELEMENT ICP ANALYSIS

Sample No.	Au	Ag	Al	As	B	Ba	Be	Bi	Ca	Cd	Co	Cr	Cu	Fe	K	La	Mg	Mn	Mo	Na	Ni	P	Pb	Sb	Se	Sr	Th	Ti	U	V	W	Zn
	ppb	ppm	%	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	%	%	ppm	%	ppm	ppm	%	ppm	%	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm
6+75N	<5	<0.5	1.76	<1	22	34	<1	<1	0.18	<1	69	12	<1	4.34	0.09	12	0.11	95	<1	0.02	74	0.20	12	<1	3	20	81	0.15	<1	87	<1	20
7+00N	<5	<0.5	0.99	<1	15	39	<1	<1	0.06	<1	22	24	7	1.28	0.14	12	0.06	105	<1	0.02	21	0.10	10	<1	<1	14	51	0.11	<1	39	<1	16
7+25N	<5	<0.5	1.70	<1	17	42	<1	<1	0.15	<1	54	17	2	3.26	0.11	2	0.15	146	<1	0.02	62	0.17	15	<1	<1	19	70	0.14	<1	75	<1	22
7+50N	<5	<0.5	1.90	<1	18	29	<1	2	0.12	<1	60	14	3	3.77	0.11	12	0.11	130	1	0.02	62	0.20	13	4	2	11	118	0.15	<1	91	<1	21
7+75N	<5	<0.5	1.08	<1	24	70	<1	4	0.17	<1	70	17	2	4.23	0.10	7	0.10	358	<1	0.02	75	0.34	12	<1	<1	23	108	0.19	<1	113	<1	29
8+00N	<5	<0.5	2.65	<1	17	297	<1	<1	0.37	<1	55	24	24	2.80	0.09	16	0.28	190	<1	0.03	65	0.31	15	<1	<1	80	33	0.13	<1	62	<1	29
8+25N	<5	<0.5	1.84	<1	26	31	<1	<1	0.17	<1	68	<1	2	4.29	0.11	9	0.15	187	<1	0.02	70	0.19	16	<1	<1	18	96	0.19	<1	95	<1	23
8+50N	<5	<0.5	1.22	<1	20	70	<1	<1	0.72	<1	34	14	7	1.64	0.07	19	0.24	168	<1	0.04	34	0.39	9	<1	1	54	100	0.11	<1	83	<1	31
8+75N	<5	<0.5	2.91	2	23	47	<1	1	0.22	<1	53	42	8	3.02	0.15	12	0.26	200	<1	0.03	67	0.19	20	<1	<1	25	169	0.11	<1	65	<1	32
9+00N	<5	<0.5	1.44	<1	22	41	<1	<1	0.11	<1	73	27	5	4.31	0.15	9	0.15	196	1	0.02	84	0.22	12	1	<1	22	86	0.19	<1	96	<1	26
9+25N	<5	<0.5	1.55	<1	20	39	<1	<1	0.16	<1	58	32	4	3.53	0.10	9	0.14	130	<1	0.02	65	0.22	13	2	<1	20	90	0.12	<1	90	<1	21
9+50N	<5	<0.5	3.33	<1	17	51	<1	<1	0.16	<1	51	14	8	2.92	0.09	<1	0.15	162	<1	0.02	54	0.18	21	<1	<1	16	65	0.10	<1	56	<1	29
9+75N	<5	<0.5	1.63	<1	20	48	<1	6	0.16	<1	44	22	6	2.71	0.07	16	0.10	114	<1	0.02	54	0.14	15	<1	2	31	16	0.14	<1	57	<1	16
10+00N	<5	<0.5	1.29	<1	20	56	<1	<1	0.14	<1	62	47	5	3.86	0.08	7	0.11	200	<1	0.02	64	0.20	13	<1	<1	20	61	0.19	<1	110	<1	23
10+25N	<5	<0.5	0.84	1	19	42	<1	1	0.08	<1	41	12	<1	2.50	0.14	<1	0.10	272	2	0.02	45	0.17	11	<1	<1	18	87	0.13	<1	91	<1	20
10+50N	<5	<0.5	1.67	3	24	50	<1	<1	0.08	<1	59	19	6	3.70	0.23	12	0.25	238	1	0.02	76	0.14	16	<1	<1	12	115	0.16	<1	64	<1	32
10+75N	<5	<0.5	1.60	<1	19	40	<1	<1	0.09	<1	51	12	1	3.16	0.16	14	0.14	263	<1	0.02	57	0.20	16	<1	<1	18	32	0.14	<1	75	<1	25
11+00N	<5	<0.5	1.39	<1	19	39	<1	4	0.12	<1	59	40	<1	3.07	0.13	19	0.17	785	<1	0.03	61	0.22	14	<1	<1	24	100	0.15	<1	70	<1	26
11+25N	<5	<0.5	1.03	2	17	55	<1	<1	0.12	<1	37	12	<1	2.22	0.19	21	0.12	174	<1	0.02	33	0.24	12	<1	<1	22	31	0.12	<1	51	<1	23
11+50N	<5	<0.5	1.17	<1	22	50	<1	2	0.15	<1	82	34	2	4.58	0.15	21	0.14	576	2	0.02	85	0.24	15	1	<1	26	329	0.28	<1	90	<1	38
11+75N	<5	<0.5	1.46	<1	21	42	<1	<1	0.14	<1	54	9	<1	3.19	0.15	14	0.20	133	2	0.02	63	0.13	17	<1	<1	17	139	0.13	<1	71	<1	26
12+00N	<5	<0.5	1.17	<1	18	38	<1	<1	0.09	<1	57	22	7	3.37	0.10	2	0.09	82	2	0.01	62	0.18	12	3	<1	15	59	0.15	<1	85	<1	19
12+25N	<5	<0.5	0.94	1	20	75	<1	2	0.19	<1	51	52	3	3.01	0.09	12	0.11	111	1	0.02	67	0.17	10	<1	<1	18	58	0.15	<1	92	<1	17
12+50N	<5	<0.5	1.22	<1	24	59	<1	<1	0.44	<1	77	27	22	4.22	0.07	5	0.24	354	2	0.03	71	0.25	13	<1	<1	38	71	0.14	<1	125	<1	33
12+75N	<5	<0.5	1.41	<1	21	122	<1	<1	0.33	<1	60	42	6	3.33	0.14	19	0.19	683	<1	0.02	53	0.18	13	3	<1	29	86	0.12	<1	74	<1	29



Loring Laboratories Ltd.

629 Beaverdam Road N.E.,
Calgary Alberta T2K 4W7
Tel: 274-2777 Fax: 275-0541



TO: 26 BT RESOURCE CO., LTD
Suite 200, 5920 McLeod Trail S.W.,
Calgary, Alberta
T2H 0K2

FILE:44243

DATE:October 26, 2001

Attn: Sudhir Jain

APPENDIX 2 (CONTINUED)

32 ELEMENT ICP ANALYSIS

Sample No.	Au	Ag	Al	As	B	Ba	Be	Bi	Ca	Cd	Co	Cr	Cu	Fe	K	La	Mg	Mn	Mo	Na	Ni	P	Pb	Sb	Se	Sr	Th	Ti	U	V	W	Zn
	ppb	ppm	%	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	%	%	ppm	%	ppm	ppm	%	ppm	%	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm
13+00N	<5	<0.5	0.64	<1	14	57	<1	2	0.21	<1	35	29	4	1.97	0.10	12	0.07	120	<1	0.03	34	0.09	11	1	<1	25	<1	0.13	<1	73	<1	19
9+00N-R	<5	<0.5	1.31	<1	22	37	<1	2	0.09	<1	71	24	3	4.23	0.14	14	0.13	190	<1	0.02	77	0.22	10	5	<1	13	103	0.17	<1	98	<1	25
STD	<5	1.9	3.36	92	20	24	<1	<1	1.18	2	70	78	64	3.99	0.28	24	1.03	567	4	0.37	192	0.05	97	26	<1	65	<1	0.07	<1	98	<1	127
BLK	<5	<0.5	<0.01	<1	<1	<1	<1	<1	<0.01	<1	<1	<1	<1	<0.01	<0.01	<1	<0.01	<1	<1	<0.01	<1	<0.01	<1	<1	<1	<1	<1	<0.01	<1	<1	<1	<1
LINE X																																
0+00S	<5	<0.5	0.52	1	19	28	<1	2	0.05	<1	31	9	7	1.84	0.37	24	0.05	279	<1	0.01	35	0.13	11	<1	<1	15	88	0.04	<1	29	<1	17
0+25S	<5	<0.5	2.30	2	25	59	<1	<1	0.21	<1	92	17	8	5.71	0.32	19	0.27	576	1	0.03	96	1.03	24	<1	<1	18	33	0.12	<1	85	<1	38
0+50S	<5	<0.5	1.44	<1	23	77	<1	1	0.11	<1	62	4	5	3.76	0.36	12	0.18	743	<1	0.03	68	0.24	21	<1	<1	20	101	0.11	<1	62	<1	32
0+75S	<5	<0.5	1.32	<1	24	50	<1	<1	0.10	<1	53	37	<1	3.09	0.27	21	0.12	351	<1	0.02	56	0.13	15	<1	<1	13	146	0.13	<1	65	<1	22
1+00S	<5	<0.5	1.41	2	24	51	<1	<1	0.16	<1	66	14	<1	4.15	0.18	9	0.14	117	<1	0.02	69	0.16	15	1	<1	20	66	0.17	<1	75	<1	19
1+25S	<5	<0.5	1.29	<1	23	53	<1	3	0.30	<1	83	29	1	5.07	0.13	7	0.22	231	<1	0.02	87	0.33	15	2	<1	27	124	0.17	<1	117	<1	27
1+50S	<5	<0.5	1.76	<1	26	39	<1	<1	0.17	<1	79	24	<1	4.75	0.20	2	0.23	221	2	0.02	87	0.27	17	<1	<1	18	76	0.14	<1	84	<1	30
1+75S	<5	<0.5	1.55	<1	25	42	<1	<1	0.11	<1	56	17	9	3.34	0.21	12	0.15	212	<1	0.02	62	0.20	15	1	<1	19	35	0.15	<1	87	<1	24
2+00S	<5	<0.5	2.05	<1	18	83	<1	<1	0.47	<1	38	29	9	1.92	0.15	21	0.30	142	<1	0.05	43	0.36	17	4	<1	46	60	0.13	<1	65	<1	34
2+25S	<5	<0.5	2.80	<1	16	56	<1	<1	0.18	<1	86	<1	3	4.00	0.34	<1	0.22	183	2	0.04	92	0.18	24	4	<1	19	133	0.21	<1	91	2	32
2+50S	<5	<0.5	2.68	<1	19	49	<1	<1	0.15	<1	82	<1	3	4.00	0.28	6	0.16	178	2	0.03	85	0.18	27	<1	<1	15	141	0.22	<1	102	<1	26
2+75S	200	<0.5	3.00	<1	14	46	<1	<1	0.18	<1	98	<1	13	4.92	0.19	<1	0.17	158	1	0.04	101	0.71	22	<1	<1	25	88	0.22	<1	100	<1	24
3+00S	<5	<0.5	4.00	<1	17	73	<1	<1	0.27	<1	99	16	8	4.61	0.30	6	0.36	275	<1	0.04	96	0.18	27	7	<1	16	162	0.27	<1	95	<1	32
3+25S	15	<0.5	2.88	2	15	83	<1	7	0.40	<1	98	20	1	4.64	0.33	6	0.28	321	1	0.04	96	0.34	20	<1	<1	40	107	0.30	<1	91	2	24
3+50S	<5	<0.5	4.32	<1	16	65	<1	<1	0.55	<1	148	26	10	4.46	0.52	<1	0.19	172	<1	0.05	108	0.29	13	3	<1	34	67	0.25	<1	99	<1	24
3+75S	50	<0.5	5.69	<1	14	77	<1	1	0.32	1	101	4	4	3.55	0.11	<1	0.28	66	<1	0.03	103	0.30	41	<1	<1	29	133	0.14	<1	72	<1	26
4+00S	10	<0.5	3.12	<1	8	102	<1	6	0.86	<1	56	<1	16	2.54	0.17	<1	0.28	209	<1	0.05	61	0.30	22	3	<1	62	42	0.16	<1	69	4	32
4+25S	10	<0.5	5.74	<1	9	57	<1	<1	0.45	3	48	4	<1	0.72	0.14	<1	0.27	204	<1	0.05	63	0.26	21	3	<1	26	84	0.06	<1	9	<1	16
4+50S	20	<0.5	2.48	<1	16	74	<1	<1	0.56	1	97	<1	6	4.62	0.31	11	0.40	591	<1	0.04	90	0.29	20	<1	<1	58	147	0.37	<1	74	<1	37



Loring Laboratories Ltd.

629 Beaverdam Road N.E.,
Calgary Alberta T2K 4W7
Tel: 274-2777 Fax: 275-0541



TO: 26 BT RESOURCE CO., LTD
Suite 200, 5920 McLeod Trail S.W.,
Calgary, Alberta
T2H 0K2

FILE:44243

DATE:October 26, 2001

Attn: Sudhir Jain

APPENDIX 2 (CONTINUED)

32 ELEMENT ICP ANALYSIS

Sample No.	Au	Ag	Al	As	B	Ba	Be	Bi	Ca	Cd	Co	Cr	Cu	Fe	K	La	Mg	Mn	Mo	Na	Ni	P	Pb	Sb	Se	Sr	Th	Ti	U	V	W	Zn
	ppb	ppm	%	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	%	%	ppm	%	ppm	ppm	%	ppm	%	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm
4+75S	<5	<0.5	0.92	2	15	76	<1	4	0.08	<1	90	<1	<1	1.52	0.07	<1	0.15	97	3	0.01	80	0.24	25	2	<1	5	81	0.08	<1	37	<1	26
5+00S	<5	<0.5	1.96	2	10	62	<1	4	0.23	<1	74	<1	11	3.61	0.24	<1	0.16	311	<1	0.03	84	0.33	18	<1	<1	30	89	0.19	<1	116	4	31
5+25S	<5	<0.5	2.96	<1	13	48	<1	4	0.44	<1	107	<1	3	5.11	0.26	6	0.28	539	2	0.07	107	0.29	23	7	<1	41	264	0.33	<1	119	<1	39
5+50S	<5	<0.5	3.80	<1	15	49	<1	<1	0.47	<1	106	28	8	5.14	0.25	6	0.29	265	<1	0.07	104	0.53	24	<1	<1	39	79	0.26	<1	98	1	36
5+75S	<5	<0.5	1.60	<1	9	43	<1	8	0.22	<1	78	12	6	3.86	0.15	<1	0.15	122	<1	0.04	93	0.45	16	8	<1	19	147	0.22	<1	82	4	25
6+00S	<5	<0.5	2.40	<1	10	49	<1	3	0.30	<1	86	<1	2	4.01	0.29	11	0.24	529	2	0.05	91	0.29	22	2	<1	33	135	0.27	<1	112	<1	37
6+25S	<5	<0.5	2.32	<1	6	55	<1	<1	0.21	<1	84	8	11	4.28	0.30	22	0.19	245	<1	0.04	91	0.28	23	4	<1	23	124	0.25	<1	105	<1	35
6+50S	<5	<0.5	3.28	<1	12	56	<1	<1	0.21	<1	96	44	13	4.24	0.28	<1	0.22	499	<1	0.04	103	0.23	25	6	<1	28	94	0.20	<1	88	2	37
6+75S	<5	<0.5	2.56	<1	15	57	<1	<1	0.25	<1	87	44	5	4.21	0.30	<1	0.23	311	2	0.05	97	0.26	21	<1	<1	27	130	0.28	<1	105	<1	34
7+00S	<5	<0.5	4.16	3	12	102	<1	<1	0.29	<1	106	16	19	4.68	0.63	<1	0.69	544	<1	0.05	127	0.23	31	3	<1	23	174	0.18	<1	68	<1	64
7+25S	50	<0.5	3.60	1	8	64	<1	4	0.21	1	89	24	9	4.21	0.38	<1	0.39	402	<1	0.04	105	0.26	25	5	<1	25	163	0.20	<1	72	2	52
7+50S	<5	<0.5	2.32	<1	7	46	<1	<1	0.34	<1	87	8	11	4.03	0.26	<1	0.29	112	<1	0.04	87	0.39	21	2	<1	30	154	0.26	<1	90	<1	36
7+75S	<5	<0.5	3.52	<1	12	50	<1	<1	0.20	<1	99	4	20	4.79	0.22	22	0.18	463	<1	0.04	98	0.23	26	2	<1	33	103	0.26	<1	119	6	40
8+00S	<5	<0.5	3.16	<1	6	54	<1	<1	0.34	<1	71	<1	10	3.48	0.16	<1	0.15	183	<1	0.03	70	0.26	21	6	<1	29	111	0.19	<1	79	<1	41
8+25S	<5	<0.5	3.56	<1	7	51	<1	1	0.24	<1	84	12	12	3.65	0.25	<1	0.20	616	3	0.04	87	0.27	23	3	<1	29	72	0.20	<1	77	2	36
8+50S	<5	<0.5	1.92	<1	11	56	<1	<1	0.49	<1	88	44	4	3.75	0.21	6	0.28	2725	<1	0.05	83	0.30	17	6	<1	68	162	0.28	<1	76	6	41
8+75S	<5	<0.5	2.80	<1	14	38	<1	13	2.05	<1	104	24	<1	4.60	0.43	6	0.96	565	<1	0.26	93	0.95	25	6	<1	115	<1	0.34	<1	91	<1	58
9+00S	<5	<0.5	2.96	<1	9	45	<1	4	0.42	<1	82	<1	11	3.77	0.21	6	0.36	469	1	0.05	86	0.47	20	<1	<1	32	85	0.22	<1	86	<1	42
9+25S	<5	<0.5	2.04	2	11	54	<1	4	0.34	<1	86	28	2	4.05	0.23	11	0.24	183	<1	0.04	106	0.43	23	5	<1	27	155	0.24	<1	109	<1	31
5+00S-R	<5	<0.5	1.72	<1	7	54	<1	<1	0.17	<1	67	<1	8	3.22	0.25	<1	0.14	305	<1	0.04	83	0.35	18	8	<1	28	69	0.17	<1	98	11	32
STD	<5	1.8	3.99	98	10	32	<1	<1	1.46	2	76	94	70	4.37	0.32	12	1.26	615	6	0.51	210	0.06	111	28	<1	84	<1	0.13	<1	105	2	137
9+50S	<5	<0.5	2.08	<1	9	39	<1	2	0.23	<1	67	4	8	3.03	0.17	<1	0.21	494	<1	0.04	86	0.36	18	7	<1	21	100	0.19	<1	74	5	30
9+75S	<5	<0.5	2.24	<1	6	39	<1	<1	0.18	1	112	4	10	5.55	0.18	6	0.21	87	<1	0.03	109	0.17	20	<1	<1	28	119	0.30	<1	116	4	31
10+00S	<5	<0.5	2.36	<1	8	58	<1	3	0.35	1	87	<1	8	4.12	0.18	22	0.20	132	<1	0.04	103	0.25	22	<1	<1	36	87	0.25	<1	75	1	31
10+25S	<5	<0.5	2.20	<1	14	37	<1	2	0.29	<1	90	<1	7	4.07	0.24	<1	0.25	351	2	0.06	101	0.34	19	5	<1	40	125	0.24	<1	91	6	44



Loring Laboratories Ltd.

629 Beaverdam Road N.E.,
Calgary Alberta T2K 4W7
Tel: 274-2777 Fax: 275-0541



TO: 26 BT RESOURCE CO., LTD
Suite 200, 5920 McLeod Trail S.W.,
Calgary, Alberta
T2H 0K2

FILE:44243

DATE:October 26, 2001

Attn: Suchir Jain

APPENDIX 2 (CONTINUED)

32 ELEMENT ICP ANALYSIS

Sample No.	Au ppb	Ag ppm	Al %	As ppm	B ppm	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	La ppm	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P %	Pb ppm	Sb ppm	Se ppm	Sr ppm	Th ppm	Ti %	U ppm	V ppm	W ppm	Zn ppm
10+50S	<5	<0.5	3.32	<1	7	44	<1	2	0.32	<1	70	<1	22	2.95	0.25	<1	0.28	346	1	0.04	84	0.38	25	8	<1	24	<1	0.16	<1	65	5	39
10+75S	<5	<0.5	2.48	1	5	57	<1	7	0.30	<1	65	<1	7	2.89	0.24	<1	0.24	357	<1	0.04	88	0.39	20	<1	<1	31	96	0.17	<1	42	6	39
11+00S	<5	<0.5	2.20	2	13	62	<1	<1	0.51	<1	88	20	28	3.91	0.27	<1	0.67	1191	<1	0.05	86	0.33	23	<1	<1	43	49	0.22	<1	72	1	54
11+25S	<5	<0.5	3.00	<1	9	63	<1	3	0.24	<1	86	4	10	3.63	0.27	<1	0.25	453	2	0.04	92	0.27	23	5	<1	25	66	0.21	<1	81	2	42
11+50S	<5	<0.5	2.12	<1	14	43	<1	<1	0.22	<1	76	16	11	3.73	0.25	11	0.25	138	<1	0.04	88	0.24	23	7	<1	30	121	0.21	<1	84	<1	36
11+75S	<5	<0.5	2.68	1	13	125	<1	<1	0.69	<1	74	28	13	3.10	0.21	11	0.36	595	<1	0.05	84	0.39	25	5	<1	54	99	0.16	<1	72	<1	51
12+00S	5	<0.5	3.24	2	4	69	<1	6	0.62	<1	83	<1	13	2.85	0.19	11	0.31	729	3	0.06	76	0.40	24	7	4	57	105	0.14	<1	49	7	54
12+25S	<5	<0.5	3.36	<1	9	62	<1	<1	0.30	<1	84	8	4	4.04	0.19	<1	0.22	194	<1	0.04	93	0.28	22	<1	<1	36	48	0.19	<1	86	<1	33
12+50S	<5	<0.5	2.32	<1	11	52	<1	6	0.19	1	91	<1	2	4.45	0.26	<1	0.18	143	<1	0.03	96	0.24	19	2	2	22	121	0.23	<1	93	5	36
12+75S	<5	<0.5	3.08	<1	8	50	<1	3	0.27	<1	84	<1	7	4.00	0.24	<1	0.21	132	<1	0.03	97	0.25	28	1	<1	23	113	0.20	<1	81	<1	40
13+00S	<5	<0.5	3.24	2	4	48	<1	<1	0.25	<1	69	16	11	3.21	0.24	6	0.32	204	<1	0.04	90	0.25	25	<1	<1	30	50	0.15	<1	65	7	41
13+25S	<5	<0.5	2.72	1	10	87	1	4	0.75	<1	88	<1	12	3.57	0.20	11	0.39	341	1	0.08	89	0.47	21	<1	<1	44	74	0.17	<1	77	4	43
13+50S	<5	<0.5	2.96	<1	8	94	<1	4	0.38	<1	69	32	23	2.89	0.27	<1	0.32	265	<1	0.05	89	0.29	22	4	<1	36	102	0.16	<1	54	6	43
13+75S	<5	<0.5	2.32	<1	6	72	<1	<1	0.51	<1	61	<1	5	2.78	0.17	<1	0.25	214	<1	0.05	93	0.41	18	2	<1	46	30	0.14	<1	72	5	32
14+00S	<5	<0.5	1.60	<1	<1	35	<1	4	0.11	<1	43	<1	14	2.00	0.17	<1	0.12	305	<1	0.03	66	0.21	12	<1	<1	25	16	0.13	<1	46	4	24
14+25S	<5	<0.5	2.88	<1	5	50	<1	<1	0.40	<1	53	<1	9	2.37	0.11	6	0.18	117	<1	0.04	77	0.33	17	<1	<1	32	64	0.14	<1	60	<1	22
14+50S	<5	<0.5	2.44	2	3	41	<1	8	0.16	<1	62	<1	10	2.94	0.20	6	0.19	153	<1	0.03	71	0.22	19	<1	2	11	68	0.16	<1	68	4	31
14+75S	<5	<0.5	2.12	<1	9	84	<1	4	0.94	<1	57	<1	7	2.46	0.13	6	0.33	198	<1	0.10	74	0.58	17	2	<1	67	<1	0.13	<1	46	6	35
15+00S	<5	<0.5	1.72	<1	4	45	<1	1	0.32	<1	76	<1	7	3.64	0.16	<1	0.17	178	<1	0.03	83	0.44	20	4	<1	24	56	0.16	<1	84	8	29
15+25S	<5	<0.5	2.00	<1	6	31	<1	10	0.25	<1	60	<1	7	2.60	0.12	<1	0.16	229	<1	0.03	71	0.29	14	<1	<1	21	32	0.14	<1	51	9	27
15+50S	<5	<0.5	2.28	<1	<1	30	<1	<1	0.27	<1	60	20	8	2.83	0.11	<1	0.15	107	<1	0.03	81	0.42	19	<1	<1	28	40	0.13	<1	58	3	23
15+75S	5	<0.5	2.56	<1	2	30	<1	4	0.14	<1	67	<1	5	3.22	0.16	<1	0.13	153	<1	0.03	84	0.31	22	3	3	22	49	0.14	<1	70	10	28
16+00S	<5	<0.5	1.96	<1	<1	31	<1	3	0.15	<1	56	16	8	2.65	0.14	<1	0.11	173	<1	0.03	76	0.22	18	<1	<1	17	<1	0.19	<1	56	8	25
16+25S	20	<0.5	2.32	<1	3	30	1	2	0.25	<1	62	<1	2	2.81	0.12	<1	0.14	326	<1	0.03	84	0.47	20	1	<1	16	80	0.14	<1	61	6	24
16+50S	<5	<0.5	1.32	<1	2	82	<1	5	0.26	<1	61	20	6	2.76	0.10	<1	0.12	774	<1	0.03	76	0.47	15	4	<1	30	50	0.14	<1	81	9	31



Loring Laboratories Ltd.

629 Beaverdam Road N.E.,
Calgary Alberta T2K 4W7
Tel: 274-2777 Fax: 275-0541



TO: 26 BT RESOURCE CO., LTD
Suite 200, 5920 McLeod Trail S.W.,
Calgary, Alberta
T2H 0K2

FILE:44243

DATE: October 26, 2001

APPENDIX 2 (CONTINUED)

Attn: Sudhir Jain

32 ELEMENT ICP ANALYSIS

Sample No.	Au	Ag	Al	As	B	Ba	Be	Bi	Ca	Cd	Co	Cr	Cu	Fe	K	La	Mg	Mn	Mo	Na	Ni	P	Pb	Sb	Se	Sr	Th	Ti	U	V	W	Zn
	ppb	ppm	%	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	%	%	ppm	%	ppm	ppm	%	ppm	%	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm
16+75S	<5	<0.5	2.04	<1	<1	38	<1	3	0.23	<1	53	4	<1	2.47	0.14	<1	0.17	234	<1	0.03	80	0.29	19	7	<1	30	50	0.13	<1	61	4	23
17+00S	<5	<0.5	1.92	<1	2	43	<1	10	0.20	<1	80	4	4	2.71	0.16	<1	0.14	295	<1	0.03	70	0.24	25	6	<1	27	83	0.17	<1	75	8	29
17+25S	<5	<0.5	1.00	<1	15	71	<1	<1	0.24	1	120	<1	15	6.69	0.26	86	0.17	300	2	0.04	81	0.37	34	<1	<1	<1	<1	0.28	<1	137	<1	40
17+50S	<5	<0.5	1.31	<1	13	100	<1	5	1.72	<1	126	<1	15	5.96	0.24	114	0.55	576	1	0.10	66	0.61	25	9	<1	103	<1	0.20	<1	125	<1	68
17+75S	5	<0.5	1.23	<1	15	85	<1	<1	0.52	<1	111	<1	5	5.35	0.28	57	0.28	1022	2	0.06	90	0.44	33	4	<1	5	<1	0.20	<1	96	<1	51
18+00S	<5	<0.5	1.51	<1	17	113	<1	<1	1.68	<1	126	<1	14	5.91	0.25	114	0.52	738	3	0.12	92	0.74	39	11	<1	106	<1	0.20	<1	114	<1	52
18+25S	<5	<0.5	1.06	1	13	78	3	2	1.57	<1	107	<1	16	5.07	0.18	76	0.38	1160	<1	0.09	73	0.62	34	12	<1	101	<1	0.20	<1	137	<1	44
18+50S	<5	<0.5	1.49	<1	9	68	<1	<1	0.44	<1	84	<1	31	4.33	0.25	86	0.25	285	4	0.05	60	0.44	39	<1	<1	<1	<1	0.22	<1	90	<1	36
18+75S	<5	<0.5	1.29	1	10	62	<1	<1	0.35	1	116	<1	16	6.51	0.31	28	0.21	385	<1	0.05	106	0.41	28	6	<1	<1	<1	0.24	<1	114	<1	29
14+25S-R	<5	<0.5	2.91	<1	11	55	<1	4	0.45	<1	55	<1	9	2.48	0.12	7	0.18	119	<1	0.06	69	0.39	20	<1	<1	31	62	0.19	<1	65	<1	24
STD	<5	1.7	3.62	105	13	34	1	<1	1.72	3	85	90	75	4.54	0.34	25	1.28	622	7	0.48	223	0.07	114	35	2	82	<1	0.12	<1	107	<1	134
BLK	<5	<0.5	<0.01	<1	<1	<1	<1	<1	<0.01	<1	<1	<1	<1	<0.01	<0.01	<1	<0.01	<1	<1	<0.01	<1	<0.01	<1	<1	<1	<1	<1	<0.01	<1	<1	<1	<1
19+00S	<5	<0.5	0.80	2	11	50	<1	<1	0.28	<1	86	<1	16	4.71	0.17	38	0.16	331	<1	0.04	61	0.55	25	8	<1	<1	2	0.21	<1	104	<1	24
19+25S	<5	<0.5	0.86	<1	8	48	<1	<1	0.22	<1	98	<1	24	5.42	0.25	38	0.17	162	5	0.04	85	0.64	31	2	<1	<1	401	0.23	<1	113	<1	26
19+50S	<5	<0.5	1.17	<1	12	60	<1	2	0.36	<1	90	<1	8	4.86	0.32	57	0.30	584	6	0.05	69	0.45	35	4	<1	12	<1	0.20	<1	55	<1	43
19+75S	<5	<0.5	1.57	<1	13	68	1	<1	0.65	<1	105	13	23	5.28	0.27	95	0.35	685	<1	0.05	82	0.62	39	<1	<1	29	257	0.21	<1	82	6	38
20+00S	<5	<0.5	1.20	<1	14	50	<1	<1	0.41	<1	98	<1	22	5.28	0.21	86	0.27	254	3	0.04	79	0.57	38	4	<1	13	<1	0.21	<1	87	<1	33
20+25S	15	<0.5	1.00	<1	14	59	1	<1	0.43	<1	99	33	18	5.18	0.19	67	0.26	523	<1	0.04	73	0.57	24	<1	<1	<1	<1	0.20	<1	82	<1	30
20+50S	<5	<0.5	1.23	<1	13	57	<1	<1	0.38	<1	95	<1	5	5.01	0.28	57	0.26	300	2	0.05	80	0.47	30	5	<1	<1	<1	0.20	<1	79	<1	38
20+75S	<5	<0.5	1.11	<1	2	48	<1	<1	0.33	<1	82	<1	17	4.65	0.25	38	0.21	292	1	0.04	63	0.51	22	11	<1	6	<1	0.18	<1	76	<1	33
21+00S	<5	<0.5	0.66	<1	10	41	<1	<1	0.19	<1	90	<1	49	4.60	0.18	38	0.20	354	2	0.03	46	0.48	18	<1	6	7	<1	0.21	<1	82	<1	44
21+25S	<5	<0.5	0.97	<1	11	45	<1	<1	0.38	<1	91	<1	18	4.99	0.17	57	0.25	261	3	0.04	91	0.74	23	<1	<1	<1	<1	0.21	<1	93	<1	38
21+50S	<5	<0.5	0.97	<1	8	47	<1	<1	0.40	<1	89	<1	23	4.95	0.19	48	0.25	354	<1	0.04	85	0.51	35	<1	<1	10	<1	0.23	<1	76	<1	39
21+75S	<5	<0.5	0.89	1	7	60	<1	<1	0.75	<1	86	<1	28	4.89	0.14	67	0.28	562	3	0.04	86	0.70	35	2	<1	<1	<1	0.20	<1	76	<1	52
22+00S	<5	<0.5	1.08	<1	7	50	<1	<1	0.40	<1	97	26	22	5.40	0.21	114	0.25	499	4	0.04	66	0.38	33	<1	<1	<1	<1	0.23	<1	87	<1	44



Loring Laboratories Ltd.

629 Beaverdam Road N.E.,
Calgary Alberta T2K 4W7
Tel: 274-2777 Fax: 275-0541



TO: 26 BT RESOURCE CO., LTD
Suite 200, 5920 McLeod Trail S.W.,
Calgary, Alberta
T2H 0K2

FILE:44243

DATE: October 26, 2001

APPENDIX 2 (CONTINUED)

Attn: Sudhir Jain

32 ELEMENT ICP ANALYSIS

Sample No.	Au	Ag	Al	As	B	Ba	Be	Bi	Ca	Cd	Co	Cr	Cu	Fe	K	La	Mg	Mn	Mo	Na	Ni	P	Pb	Sb	Se	Sr	Th	Ti	U	V	W	Zn
	ppb	ppm	%	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	%	%	ppm	%	ppm	ppm	%	ppm	%	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm
22+25S	<5	<0.5	1.48	<1	11	53	<1	<1	0.59	<1	112	26	15	6.04	0.22	105	0.32	384	<1	0.04	86	0.46	33	<1	<1	33	<1	0.25	<1	84	<1	46
22+50S	<5	<0.5	1.06	<1	7	58	<1	<1	0.63	<1	93	<1	22	4.86	0.25	105	0.38	377	2	0.04	88	0.52	34	<1	<1	12	<1	0.23	<1	87	<1	46
22+75S	<5	<0.5	1.23	<1	12	59	<1	<1	0.59	<1	96	<1	31	5.12	0.21	76	0.35	923	2	0.04	76	0.43	43	<1	<1	5	<1	0.32	<1	82	<1	56
23+00S	<5	<0.5	0.94	3	15	52	<1	1	0.43	<1	94	<1	31	5.03	0.20	19	0.28	431	<1	0.04	82	0.39	37	<1	<1	<1	<1	0.28	<1	73	<1	51
19+00S-R	<5	<0.5	0.80	1	19	45	<1	<1	0.29	<1	84	<1	14	4.65	0.15	37	0.16	324	<1	0.04	56	0.59	29	7	<1	<1	2	0.21	<1	110	<1	25
STD	<5	1.8	3.48	114	27	31	2	<1	2.39	3	139	58	89	6.71	0.34	15	1.75	599	5	0.35	226	0.06	130	31	3	75	<1	0.12	<1	108	<1	111
BLK	<5	<0.5	<0.01	<1	<1	<1	<1	<1	<0.01	<1	<1	<1	<1	<0.01	<0.01	<1	<0.01	<1	<1	<0.01	<1	<0.01	<1	<1	<1	<1	<0.01	<1	<1	<1	<1	

Gold analyzed by Fireassay / A.A. finish.

"R" Denotes duplicate sample analyzed.

0.500 Gram sample is digested with Aqua Regia at 95 C for one hour and bulked to 10 ml with distilled water.

Partial dissolution for Al, B, Ba, Ca, Cr, Fe, K, La, Mg, Mn, Na, P, Sr, Ti, and W.

Certified by:



Loring Laboratories Ltd.

629 Beaverdam Road N.E.,
Calgary Alberta T2K 4W7
Tel: 274-2777 Fax: 275-0541



TO: 26 BT RESOURCE CO., LTD
Suite 200, 5920 McLeod Trail S.W.,
Calgary, Alberta
T2H 0K2

FILE:44243

DATE:October 26, 2001

Attn: Sudhir Jain

APPENDIX 2 (CONTINUED)

PGM ANALYSIS

Sample No.	Au ppb	Pd ppb	Pt ppb	Rh ppb
S-131	<5	<5	<5	<5
S-132	<5	<5	<5	<5
S-133	<5	<5	<5	<5
S-134	125	<5	<5	<5
S-135	<5	<5	<5	<5
S-136	<5	<5	<5	<5
S-137	<5	<5	<5	<5
S-138	6	<5	<5	<5
S-139	<5	<5	<5	<5
S-140	<5	<5	<5	<5
S-141	<5	<5	<5	<5
S-142	<5	<5	<5	<5
S-143	10	<5	<5	<5
S-144	<5	<5	<5	<5
S-145	<5	<5	<5	<5
S-146	<5	<5	<5	<5
S-147	<5	<5	<5	<5
S-148	<5	<5	<5	<5
S-149	<5	<5	<5	<5
S-150	<5	<5	<5	<5
S-151	<5	<5	<5	<5
S-152	<5	<5	<5	<5
S-153	15	<5	<5	<5
S-154	<5	<5	<5	<5
S-155	<5	<5	<5	<5
S-156	15	<5	<5	<5

Samples analyzed by fire assay / ICP.

Certified by: _____



Loring Laboratories Ltd.

629 Beaverdam Road N.E.,
Calgary Alberta T2K 4W7
Tel: 274-2777 Fax: 275-0541



TO: **26 BT RESOURCE CO., LTD**
Suite 200, 5920 McLeod Trail S.W.,
Calgary, Alberta
T2H 0K2

FILE: 44243

DATE: October 26, 2001

APPENDIX 2 (CONTINUED)

Attn: Sudhir Jain

WHOLE ROCK ANALYSIS BY ICP

Sample No.	Al ₂ O ₃ %	Ba ppm	CaO %	Cr ppm	Fe ₂ O ₃ %	K ₂ O %	MgO %	MnO %	Na ₂ O %	Ni ppm	P ₂ O ₅ %	SO ₃ %	SiO ₂ %	Sr ppm	TiO ₂ %	V ppm	LOI %	SUM %
S-131	10.12	2407	9.79	104	20.16	0.71	4.85	0.30	2.02	98	0.423	0.44	36.45	484	8.06	389	1.88	95.20
S-132	8.74	314	8.21	96	26.04	0.58	4.18	0.38	1.33	50	0.481	0.14	36.01	396	9.16	429	2.26	97.54
S-133	8.12	304	7.68	99	25.93	0.56	4.47	0.34	1.42	64	0.400	0.12	36.21	371	9.11	525	1.63	96.07
S-134	8.18	568	7.23	266	21.69	0.99	3.80	0.31	1.42	129	0.685	0.14	37.26	301	6.01	289	8.39	96.16
S-135	9.61	556	7.78	55	23.87	0.70	4.14	0.25	2.02	66	0.656	0.14	38.84	457	6.23	373	2.73	96.58
S-136	8.91	380	6.88	77	29.12	0.55	4.10	0.35	1.43	45	0.753	0.12	31.98	346	10.08	594	2.49	96.79
S-137	8.16	371	6.91	49	29.34	0.51	4.15	0.32	1.41	45	0.596	0.13	33.80	333	9.78	666	0.75	95.94
S-138	8.14	381	7.38	74	27.76	0.56	4.21	0.31	1.48	56	0.571	0.12	35.63	339	8.85	524	1.33	96.43
S-139	9.42	487	7.96	140	24.94	0.71	4.19	0.26	1.81	105	0.489	0.14	37.82	422	6.52	331	2.25	96.64
S-140	8.98	421	7.68	49	29.37	0.48	4.53	0.34	1.40	53	0.500	0.12	32.02	356	10.02	612	0.62	96.19
S-141	8.31	295	13.22	66	21.40	0.53	6.49	0.33	1.83	71	0.552	0.17	38.31	468	4.03	214	2.34	97.61
S-142	8.09	187	9.86	71	24.75	0.49	5.10	0.36	1.33	37	0.604	0.18	35.62	411	8.39	461	1.75	96.58
S-143	8.84	296	8.19	74	27.96	0.66	3.88	0.42	1.50	36	0.988	0.17	32.88	377	9.42	455	1.53	96.52
S-144	9.10	1107	9.54	323	23.13	0.72	4.84	0.41	1.62	172	0.703	0.17	35.82	291	9.29	371	1.67	97.09
S-145	7.71	198	7.17	86	29.92	0.50	4.29	0.34	1.25	11	0.363	0.12	35.60	330	9.56	731	0.36	97.20
S-146	8.92	410	8.69	129	28.33	0.59	4.74	0.25	1.51	156	0.345	0.13	38.03	431	5.94	463	1.23	98.77
S-147	9.41	351	8.02	104	24.99	0.56	4.37	0.27	1.47	47	0.359	0.14	39.41	415	7.13	469	1.41	97.66
S-148	8.94	340	8.14	107	25.59	0.57	4.49	0.28	1.41	55	0.343	0.16	38.40	413	7.39	526	1.19	97.02
S-149	8.94	284	8.15	82	24.52	0.50	4.52	0.29	1.40	46	0.406	0.14	38.84	387	8.26	439	1.63	97.71
S-150	9.89	368	6.90	71	21.35	0.64	3.52	0.24	1.66	49	0.448	0.11	42.70	412	7.17	269	2.61	97.34
S-151	9.31	338	7.96	71	21.33	0.92	4.27	0.24	1.60	42	0.560	0.13	42.98	415	6.65	330	1.76	97.82
S-152	8.89	357	7.51	145	24.90	0.60	4.30	0.28	1.44	59	0.532	0.20	39.43	362	8.12	466	1.42	97.69
S-153	10.08	422	7.33	184	20.71	0.75	4.07	0.22	1.81	77	0.596	0.18	42.47	413	4.90	298	3.40	96.64
S-154	9.71	421	6.66	96	20.58	0.74	3.52	0.24	1.68	41	0.430	0.13	44.02	395	5.46	346	3.35	96.63
S-155	8.85	499	5.52	183	18.62	0.95	3.04	0.20	1.55	40	0.433	0.13	48.62	318	4.86	230	4.32	97.22
S-156	8.92	579	3.54	323	13.52	1.09	1.94	0.15	1.62	27	0.269	0.15	59.28	272	2.01	47	4.60	97.21
S-147-R	9.60	326	8.13	126	24.95	0.62	4.29	0.28	1.50	46	0.387	0.14	39.67	420	7.11	472	1.41	98.17

0.2g. Sample fused with lithium metaborate, dissolved in 5% HNO₃, and analyzed by ICP.

Certified by:

To : 26 BT RESOURCE CO. LTD.
 200, 5920 McLeod Trail S.W.
 Calgary, Alberta
 T2H 0K2
 ATTN: Sudhir Jain



File No : 44308
 Date : November 20, 2001
 Samples : Rock
 Project :
 P.O.#


Certificate of Assay
Loring Laboratories Ltd.

629 Beaverdam Road, NE Calgary Alberta T2K 4W7
 Tel: (403)274-2777 Fax: (403)275-0541

APPENDIX 2 (CONTINUED)

Sample No.	Au ppb	Pd ppb	Pt ppb
"PGM Analysis"			
R - 258	19	< 5	< 5
R - 259	12	< 5	< 5
R - 260	5	< 5	< 5
R - 261	< 5	< 5	< 5
R - 262	< 5	< 5	< 5
R - 263	< 5	< 5	< 5
R - 264	< 5	< 5	< 5
R - 265	< 5	< 5	< 5
R - 266	5	< 5	< 5
R - 267	5	< 5	< 5
R - 268	5	< 5	< 5
R - 269	< 5	< 5	< 5
R - 270	6	< 5	< 5
R - 271	42	< 5	< 5

I HEREBY CERTIFY that the above results are those assays made by me upon the herein described samples :

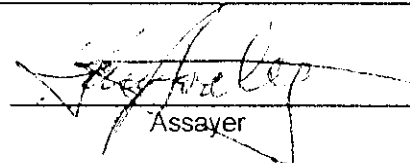
 Assayer

Rejects and pulps are retained for one month unless specific arrangements are made in advance.



Loring Laboratories Ltd.

629 Beaverdam Road N.E.,
Calgary Alberta T2K 4W7
Tel: 274-2777 Fax: 275-0541



TO: 26 BT RESOURCE CO., LTD
Suite 200, 5920 McLeod Trail S.W.,
Calgary, Alberta
T2H 0K2

FILE: 44126-1

DATE: December 13, 2001

APPENDIX 2A

Attn: Sudhir Jain

WHOLE ROCK ANALYSIS BY ICP

Sample No.	Al ₂ O ₃ %	Ba ppm	CaO %	Cr ppm	Fe ₂ O ₃ %	K ₂ O %	MgO %	MnO %	Na ₂ O %	Ni ppm	P ₂ O ₅ %	SO ₃ %	SiO ₂ %	Sr ppm	TiO ₂ %	V ₂ O ₅ %	LOI %	SUM %
R- 251	13.37	631	10.87	370	16.70	1.49	9.89	0.20	1.87	224	0.393	0.27	40.51	341	2.28	0.03	1.92	99.83
R- 252	12.37	224	12.94	87	19.83	0.69	5.90	0.25	1.72	279	0.552	1.02	37.02	426	3.29	0.03	4.24	99.94
R- 253	15.18	353	13.94	21	16.79	0.72	4.02	0.26	2.93	14	1.854	0.29	39.79	1722	2.74	0.02	0.51	99.24
R- 254	12.77	427	16.83	260	16.74	0.62	8.05	0.18	1.25	107	0.062	0.20	38.38	526	1.99	0.06	2.29	99.55
R- 255	12.38	592	14.62	<2	22.29	1.02	5.56	0.26	1.47	26	1.498	0.18	34.59	755	4.01	0.06	1.86	99.88
R- 256	18.89	880	14.59	80	14.01	0.48	3.82	0.14	2.65	42	0.112	0.32	41.47	989	2.08	0.05	0.94	99.74
R- 257	13.56	188	26.75	82	6.12	0.17	13.06	0.13	0.27	10	0.008	0.29	36.97	201	0.88	<0.01	1.24	99.49

0.2g sample fused with lithium metaborate and dissolved in 5%HNO₃.

Certified by:



Loring Laboratories Ltd.

629 Beaverdam Road N.E.,
Calgary Alberta T2K 4W7
Tel: 274-2777 Fax: 275-0541



TO: 26 BT RESOURCE CO., LTD
Suite 200, 5920 McLeod Trail S.W.,
Calgary, Alberta
T2H 0K2

FILE: 44126

DATE: December 13, 2001

APPENDIX 2A (CONTINUED)

Attn: Sudhir Jain

PGM ANALYSIS

Sample No.	Au ppb	Pd ppb	Pt ppb	Rh ppb
R - 251	<5	<5	<5	<5
R - 252	5	<5	<5	<5
R - 253	<5	<5	<5	<5
R - 254	<5	<5	<5	<5
R - 255	<5	<5	<5	<5
R - 256	<5	<5	<5	<5
R - 257	<5	<5	<5	<5

Certified by:



Loring Laboratories Ltd.

629 Beaverdam Road N.E.,
Calgary Alberta T2K 4W7
Tel: 274-2777 Fax: 275-0541



TO: 26 BT RESOURCE CO., LTD
Suite 200, 5920 McLeod Trail S.W.,
Calgary, Alberta
T2H 0K2

FILE:44360

APPENDIX 3


DATE:December 3, 2001

Attn: Sudhir Jain

30 ELEMENT ICP ANALYSIS

Sample No.	Ag ppm	Al %	As ppm	Au ppm	B ppm	Ba ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	La ppm	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P %	Pb ppm	Sb ppm	Sr ppm	Th ppm	Ti %	U ppm	V ppm	W ppm	Zn ppm
95-2 18'	<0.5	1.36	<1	<1	41	3279	6	1.51	1	54	2	8	5.48	0.82	53	1.02	261	7	0.10	44	0.48	8	1	41	<1	0.38	<1	50	1	26
95-2 53'	<0.5	1.14	<1	<1	41	2760	4	1.25	1	37	2	2	4.14	0.61	45	0.77	277	6	0.10	36	0.58	3	2	31	<1	0.43	<1	40	1	32
95-3 58'	<0.5	3.70	5	<1	32	41	3	2.30	1	25	2	11	2.96	0.17	59	0.31	657	2	0.10	19	0.03	20	4	122	3	0.04	<1	<1	<1	39
95-3 119'	<0.5	1.85	<1	<1	26	<1	2	0.85	1	25	<1	10	2.94	0.13	88	0.28	839	3	0.07	19	0.04	16	2	48	<1	0.12	<1	<1	1	60

0.500 Gram sample is digested with Aqua Regia at 95 C for one hour and bulked to 10 ml with distilled water.
Partial dissolution for Al, B, Ba, Ca, Cr, Fe, K, La, Mg, Mn, Na, P, Sr, Ti, and W.

Certified by: 

To : 26 BT RESOURCE CO. LTD.
200, 5920 MacLeod Trail S.W.
Calgary, Alberta
T2H 0K2
ATTN: Sudhir Jain



File No : 4 4 3 6 0
Date : December 5, 2001
Samples :
Project :
P.O.#

Certificate of Assay
Loring Laboratories Ltd.

629 Beaverdam Road, NE Calgary Alberta T2K 4W7
Tel: (403)274-2777 Fax: (403)275-0541

APPENDIX 3 (CONTINUED)

Sample No.	Au ppb
95-2- 18'	120
95-2- 53'	< 5
DDH-95-3-58'	10
DDH-95-3-119'	10

I HEREBY CERTIFY that the above results are those assays
made by me upon the herein described samples :


Assayer

Rejects and pulps are retained for one month unless specific arrangements are made in advance.

To : 26 BT RESOURCE CO. LTD.
 200, 5920 MacLeod Trail S.W.
 Calgary, Alberta
 T2H 0K2
 ATTN: Sudhir Jain



File No : 44360
 Date : December 5, 2001
 Samples :
 Project :
 P.O.#


Certificate of Assay
Loring Laboratories Ltd.

629 Beaverdam Road, NE Calgary Alberta T2K 4W7
 Tel: (403)274-2777 Fax: (403)275-0541

APPENDIX 4A

Sample No.	Au ppb
"Geochemical Analysis"	
95-2- 10-15	20
95-2- 15-20	10
95-2- 25-30	5
95-2- 30-35	< 5
95-2- 35-40	< 5
95-2- 40-45	< 5
95-2- 45-50	< 5
95-2- 50-55	< 5
95-2- 55-60	< 5
95-2- 60-65	< 5
95-2- 65-70	< 5
95-2- 70-75	10
95-2- 75-80	35
95-2- 80-85	30
95-2- 85-90	400
95-2- 90-95	25
95-2- 95-100	< 5
95-2- 100-105	< 5
95-2- 105-110	< 5
95-2- 110-115	< 5
95-2- 115-120	< 5

I HEREBY CERTIFY that the above results are those assays
 made by me upon the herein described samples :

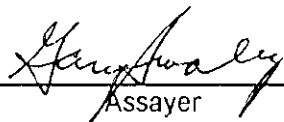
 Assayer

Rejects and pulps are retained for one month unless specific arrangements are made in advance.

To : 26 BT RESOURCE CO. LTD.
200, 5920 MacLeod Trail S.W.
Calgary, Alberta
T2H 0K2
ATTN: Sudhir Jain



File No : 4 4 1 2 6-3
Date : January 15, 2002
Samples :
Project :
P.O.#


Certificate of Assay Loring Laboratories Ltd.

629 Beaverdam Road, NE Calgary Alberta T2K 4W7
Tel: (403)274-2777 Fax: (403)275-0541

APPENDIX 4B

Sample No.	Au ppb	Fraction %
S105 Magnetics	900	17.82
S105 Non-Magnetics	700	82.18

I HEREBY CERTIFY that the above results are those assays
made by me upon the herein described samples :

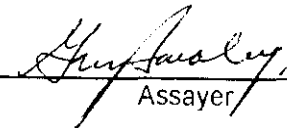
Assayer

Rejects and pulps are retained for one month unless specific arrangements are made in advance.



Loring Laboratories Ltd.

629 Beaverdam Road N.E.,
Calgary Alberta T2K 4W7
Tel: 274-2777 Fax: 275-0541



TO: 26 BT RESOURCE CO., LTD
Suite 200, 5920 McLeod Trail S.W.,
Calgary, Alberta
T2H 0K2

FILE: 44806

DATE: July 10, 2002

APPENDIX 4C

Attn: Sudhir Jain

PGM ANALYSIS

Drill Hole: 96 - 3

Sample No.	Au ppb	Pd ppb	Pt ppb	Rh ppb
20-25	15	<5	5	<5
25-30	15	<5	25	<5
30-35	25	<5	20	<5
35-40	<5	<5	15	<5
40-45	<5	<5	<5	<5
45-50	<5	<5	<5	<5
50-55	<5	52	<5	<5
55-60	<5	<5	<5	<5
60-65	10	24	<5	<5
65-70	<5	<5	<5	<5
70-75	<5	<5	<5	<5
75-80	<5	<5	<5	<5
80-85	10	<5	<5	<5
85-90	<5	<5	<5	<5
90-95	<5	<5	<5	<5
95-100	<5	<5	<5	<5
100-105	<5	<5	<5	<5
105-110	<5	<5	<5	<5
110-115	<5	<5	<5	<5
115-120	<5	<5	<5	<5
120-125	<5	<5	<5	<5
125-130	<5	<5	5	5
130-135	<5	<5	15	15
135-140	5	<5	<5	<5
140-145	10	<5	<5	<5
145-150	55	<5	<5	<5
150-155	<5	<5	<5	<5
155-160	<5	<5	<5	<5
160-165	<5	<5	<5	<5
165-170	<5	<5	<5	<5



Loring Laboratories Ltd.

629 Beaverdam Road N.E.,
Calgary Alberta T2K 4W7
Tel: 274-2777 Fax: 276-0541



TO: 26 BT RESOURCE CO., LTD
Suite 200, 5920 McLeod Trail S.W.,
Calgary, Alberta
T2H 0K2

FILE: 44806

DATE: July 10, 2002

APPENDIX 4C (CONTINUED)

Attn: Sudhir Jain

PGM ANALYSIS

Drill Hole: 96 - 3

Sample No.	Au ppb	Pd ppb	Pt ppb	Rh ppb
170-175	<5	<5	<5	<5
175-180	<5	<5	<5	<5
180-185	5	<5	<5	<5
185-190	<5	<5	<5	<5
190-195	35	<5	<5	<5
195-200	10	<5	<5	<5
200-205	5	<5	<5	<5
205-210	5	<5	<5	<5
210-215	15	<5	<5	<5
215-220	<5	<5	<5	<5
220-225	<5	<5	<5	<5
225-230	<5	<5	<5	<5
230-235	<5	<5	<5	<5
235-240	<5	<5	<5	<5
240-245	5	<5	<5	<5
245-250	<5	<5	<5	<5
250	<5	<5	<5	<5
251	<5	<5	<5	<5
252	<5	<5	<5	<5
253	<5	<5	<5	<5
254	<5	<5	<5	<5
255	<5	<5	<5	<5
256	<5	<5	<5	<5
257	<5	<5	<5	<5
258	<5	<5	<5	<5
259	<5	<5	<5	<5
260	<5	<5	<5	<5
261	<5	<5	<5	<5
262	<5	<5	<5	<5
263	<5	<5	<5	<5



Loring Laboratories Ltd.

629 Beaverdam Road N.E.,
Calgary Alberta T2K 4W7
Tel: 274-2777 Fax: 275-0541



TO: 26 BT RESOURCE CO., LTD
Suite 200, 5920 McLeod Trail S.W.,
Calgary, Alberta
T2H 0K2

FILE: 44806

DATE: July 10, 2002

APPENDIX 4C (CONTINUED)

Attn: Sudhir Jain

PGM ANALYSIS

Drill Hole: 96 - 3

Sample No.	Au ppb	Pd ppb	Pt ppb	Rh ppb
264-266	<5	<5	<5	<5
266-268	<5	<5	<5	<5
268	<5	<5	<5	<5
269	<5	<5	<5	<5
270	<5	<5	<5	<5
271	<5	<5	<5	<5
272	<5	<5	<5	<5
273	<5	<5	<5	<5
274	15	<5	<5	<5
275	<5	<5	<5	<5
276	<5	<5	<5	<5
277	<5	<5	<5	<5
278	<5	<5	<5	<5
279	<5	<5	<5	<5
280	<5	<5	<5	<5
281	<5	<5	<5	<5
282	<5	<5	<5	<5
283	<5	<5	<5	<5
284	<5	<5	<5	<5
270-275	<5	<5	<5	<5
275-280	<5	<5	<5	<5
280-285	<5	<5	<5	<5
285-290	<5	<5	<5	<5
290-295	<5	<5	<5	<5
295-300	<5	<5	<5	<5
PGM- Std.(333ppb)	329	291	308	321

Certified by: *[Signature]*

Loring Laboratories Ltd.

629 Beaverdam Road N.E.,
Calgary Alberta T2K 4W7
Tel: 274-2777 Fax: 275-0541

TO: 26 BT RESOURCE CO., LTD
Suite 200, 5920 McLeod Trail S.W.,
Calgary, Alberta
T2H 0K2

FILE: 44652

DATE: May 16, 2002

APPENDIX 5

Attn: Sudhir Jain

PGM ANALYSIS

Sample No.	Au ppb	Pd ppb	Pt ppb	Rh ppb
R - 2	127	<5	<5	<5
R - 3	6	8	<5	<5
R - 5	6	<5	<5	<5
R - 7	10	<5	<5	<5
R - 9	36	<5	<5	<5
R - 10	<5	<5	<5	<5
R - 11	<5	<5	<5	<5
R - 12	<5	<5	<5	<5
R - 13	146	<5	<5	<5
R - 15	310	<5	<5	<5
R - 16	7	<5	<5	<5
R - 17	<5	<5	<5	<5
R - 18	<5	<5	<5	<5
R - 20	<5	<5	<5	<5
R - 21	<5	<5	<5	<5
R - 24	<5	<5	<5	<5
R - 25	<5	<5	<5	<5
R - 26	<5	<5	<5	<5
R - 27	18	<5	<5	<5
R - 28	<5	<5	<5	<5
R - 30	<5	<5	<5	<5
R - 32	<5	<5	<5	<5
R - 33	<5	<5	<5	<5
R - 41	<5	<5	<5	<5
R - 43	36	<5	<5	<5
R - 44	<5	<5	<5	<5
R - 45	<5	<5	<5	<5
R - 51	<5	<5	<5	<5
R - 52	<5	<5	<5	<5
R - 53	<5	<5	<5	<5

Loring Laboratories Ltd.

629 Beaverdam Road N.E.,
Calgary Alberta T2K 4W7
Tel: 274-2777 Fax: 275-0541

TO: 26 BT RESOURCE CO., LTD
Suite 200, 5920 McLeod Trail S.W.,
Calgary, Alberta
T2H 0K2

FILE: 44652

DATE: May 16, 2002

APPENDIX 5 (CONTINUED)

Attn: Sudhir Jain

PGM ANALYSIS

Sample No.	Au ppb	Pd ppb	Pt ppb	Rh ppb
R - 55	<5	<5	<5	<5
R - 57	6	<5	<5	<5
R - 58	<5	<5	<5	<5
R - 59	<5	<5	<5	<5
R - 60	<5	<5	<5	<5
R - 61	<5	<5	<5	<5
R - 62	<5	<5	<5	<5
R - 64	141	<5	<5	<5
R - 66	12	<5	<5	<5
R - 67	<5	<5	<5	<5
R - 69	<5	<5	<5	<5
R - 71	<5	<5	<5	<5
R - 72	18	<5	<5	<5
R - 73	<5	<5	<5	<5
R - 74	<5	<5	<5	<5
R - 74A	<5	<5	<5	<5
R - 75	<5	<5	<5	<5
R - 76	<5	<5	<5	<5
R - 77	<5	<5	<5	<5
R - 79	<5	<5	<5	<5
R - 80	<5	<5	<5	<5
R - 81	<5	<5	<5	<5
R - 82	<5	<5	<5	<5
R - 83	<5	<5	<5	<5
R - 85	<5	<5	<5	<5
R - 85A	<5	<5	<5	<5
R - 86	<5	<5	<5	<5
R - 87	<5	<5	<5	<5
R - 89	<5	<5	<5	<5
R - 90	<5	<5	<5	<5

Loring Laboratories Ltd.

629 Beaverdam Road N.E.,
 Calgary Alberta T2K 4W7
 Tel: 274-2777 Fax: 275-0541

TO: 26 BT RESOURCE CO., LTD
 Suite 200, 5920 McLeod Trail S.W.,
 Calgary, Alberta
 T2H 0K2

FILE: 44652

DATE: May 16, 2002

APPENDIX 5 (CONTINUED)

Attn: Sudhir Jain

PGM ANALYSIS

Sample No.	Au ppb	Pd ppb	Pt ppb	Rh ppb
R - 91	<5	<5	<5	<5
R - 92	<5	<5	<5	<5
R - 93	<5	<5	<5	<5
R - 94	<5	<5	<5	<5
R - 95	<5	<5	<5	<5
R - 96	<5	<5	<5	<5
R - 97	<5	<5	<5	<5
R - 103	6	<5	<5	<5
R - 105	<5	<5	<5	<5
R - 107	6	<5	<5	<5
R - 114	<5	<5	<5	<5
R - 115	<5	<5	<5	<5
R - 116	10	<5	<5	<5
R - 117	10	<5	<5	<5
R - 123	<5	<5	<5	<5
R - 126	<5	<5	<5	<5
R - 128	<5	<5	<5	<5
R - 130	12	<5	<5	<5
R - 132	30	<5	<5	<5
R - 138	17	<5	<5	<5
R - 139	<5	<5	<5	<5
R - 140	<5	<5	<5	<5
R - 142	<5	<5	<5	<5
R - 143	<5	<5	<5	<5
R - 145	<5	<5	<5	<5
R - 146	<5	<5	<5	<5
R - 147	<5	<5	<5	<5
R - 148	<5	<5	<5	<5
R - 149	<5	<5	<5	<5
R - 151	<5	<5	<5	<5

Loring Laboratories Ltd.

629 Beaverdam Road N.E.,

Calgary Alberta T2K 4W7

Tel: 274-2777 Fax: 275-0541

TO: 26 BT RESOURCE CO., LTD
Suite 200, 5920 McLeod Trail S.W.,
Calgary, Alberta
T2H 0K2

FILE: 44652

DATE: May 16, 2002

APPENDIX 5 (CONTINUED)

Attn: Sudhir Jain

PGM ANALYSIS

Sample No.	Au ppb	Pd ppb	Pt ppb	Rh ppb
R - 152	<5	<5	<5	<5
R - 156	<5	<5	<5	<5
R - 158	5	<5	<5	<5
R - 164	<5	<5	<5	<5
R - 165	<5	<5	<5	<5
R - 168	<5	<5	<5	<5
R - 170A	<5	<5	<5	<5
R - 170B	<5	<5	<5	<5
R - 176	<5	<5	<5	<5
R - 180	<5	<5	<5	<5
R - 182	<5	<5	<5	<5
R - 183	<5	<5	<5	<5
R - 184	<5	<5	<5	<5
R - 185	<5	<5	<5	<5
R - 186	<5	10	<5	<5
R - 189	<5	<5	<5	<5
R - 191	<5	<5	<5	<5
R - 193	<5	<5	<5	<5
R - 195	5	<5	<5	<5
R - 196	<5	<5	<5	<5
R - 199	<5	<5	<5	<5
R - 200	<5	<5	<5	<5
R - 203	15	<5	<5	<5
R - 205	<5	<5	<5	<5
R - 206	<5	<5	<5	<5
R - 207	<5	<5	<5	<5
R - 209	<5	<5	<5	<5
R - 210	<5	<5	<5	<5
R - 215	<5	<5	<5	<5
R - 217	<5	<5	<5	<5

Loring Laboratories Ltd.

629 Beaverdam Road N.E.,
 Calgary Alberta T2K 4W7
 Tel: 274-2777 Fax: 275-0541

TO: **26 BT RESOURCE CO., LTD**
 Suite 200, 5920 McLeod Trail S.W.,
 Calgary, Alberta
 T2H 0K2

FILE: 44652

DATE: May 16, 2002

APPENDIX 5 (CONTINUED)

Attn: Sudhir Jain

PGM ANALYSIS

Sample No.	Au ppb	Pd ppb	Pt ppb	Rh ppb
R - 218	<5	<5	<5	<5
R - 219	<5	<5	<5	<5
R - 220	<5	<5	<5	<5
R - 221	<5	<5	<5	<5
R - 226	<5	<5	<5	<5
R - 228	<5	<5	<5	<5
R - 229	<5	<5	<5	<5
? - 232	<5	<5	<5	<5
R - 233	18	<5	<5	<5
R - 234	<5	<5	<5	<5
R - 235	<5	<5	<5	<5
R - 237	<5	<5	<5	<5
R - 238	<5	<5	<5	<5
R - 240	<5	<5	<5	<5
R - 243	<5	<5	<5	<5
R - 246	<5	<5	<5	<5
R - 248	<5	<5	<5	<5
R - 249	<5	<5	<5	<5
R - 250	10	<5	<5	<5
S90 - 1	<5	<5	<5	<5
S90 - 2A	<5	<5	<5	<5
S90 - 2B	<5	<5	<5	<5
S90 - 3	<5	<5	<5	<5
S90 - 6	<5	<5	<5	<5
S90 - 7	10	<5	<5	<5
S90 - 8	<5	<5	<5	<5
S90 - 9	5	<5	<5	<5
S90 - 16	<5	<5	<5	<5
S90 - 17	<5	<5	<5	<5

Loring Laboratories Ltd.

629 Beaverdam Road N.E.,
 Calgary Alberta T2K 4W7
 Tel: 274-2777 Fax: 275-0541

TO: **26 BT RESOURCE CO., LTD**
 Suite 200, 5920 McLeod Trail S.W.,
 Calgary, Alberta
 T2H 0K2

FILE: 44652

DATE: May 16, 2002

APPENDIX 5 (CONTINUED)

Attn: Sudhir Jain

PGM ANALYSIS

Sample No.	Au ppb	Pd ppb	Pt ppb	Rh ppb
S90 - 18	<5	<5	<5	<5
S90 - 20	<5	<5	<5	<5
S90 - 21	<5	<5	<5	<5
S90 - 22A	<5	<5	<5	<5
S90 - 22B	<5	<5	<5	<5
S90 - 24	<5	<5	<5	<5
S90 - 27	<5	<5	<5	<5
S90 - 28	<5	<5	<5	<5
S90 - 32	<5	<5	<5	<5
S90 - 34	<5	<5	<5	<5
S90 - 35	<5	<5	<5	<5
S90 - 36	<5	<5	<5	<5
S - 37	<5	<5	<5	<5
S - 38	<5	<5	<5	<5
S - 40	<5	<5	<5	<5
S - 41	<5	<5	<5	<5
S - 42	15	<5	<5	<5
S - 43	12	<5	<5	<5
S - 45	<5	<5	<5	<5
S - 47	<5	<5	<5	<5
S - 48	<5	<5	<5	<5
S - 49	<5	<5	<5	<5
S - 51	65	15	11	<5
S - 55	85	10	13	<5

Certified by: _____

Loring Laboratories Ltd.

629 Beaverdam Road N.E.,
 Calgary Alberta T2K 4W7
 Tel: 274-2777 Fax: 275-0541

TO: 26 BT RESOURCE CO., LTD
 Suite 200, 5920 McLeod Trail S.W.,
 Calgary, Alberta
 T2H 0K2

FILE: 44988

DATE: October 2, 2002

APPENDIX 6

Attn: Sudhir Jain

PGM ANALYSIS

Sample No.	Au ppb	Pd ppb	Pt ppb	Rh ppb
0+00N 30+25E	<5	<5	<5	<5
30+50E	<5	<5	<5	<5
30+75E	<5	<5	<5	<5
31+00E	<5	<5	<5	<5
31+25E	9	<5	<5	<5
31+50E	<5	<5	<5	<5
31+75E	<5	<5	<5	<5
32+00E	<5	<5	<5	<5
32+25E	<5	<5	<5	<5
32+50E	<5	<5	<5	<5
32+75E	<5	<5	<5	<5
33+00E	41	<5	<5	<5
33+25E	<5	<5	<5	<5
33+50E	<5	<5	<5	<5
33+75E	<5	<5	<5	<5
34+00E	<5	<5	<5	<5
34+25E	<5	<5	<5	<5
34+50E	<5	<5	<5	<5
34+75E	<5	<5	<5	<5
35+00E	<5	<5	<5	<5
35+25E	<5	<5	<5	<5
35+50E	<5	<5	<5	<5
35+75E	126	<5	<5	<5
36+00E	<5	<5	<5	<5
36+25E	<5	<5	<5	<5
36+50E	68	<5	<5	<5
36+75E	20	<5	<5	<5
37+00S	<5	<5	<5	<5
37+25S	<5	<5	<5	<5
37+50S	<5	<5	<5	<5

Certified by: _____

Loring Laboratories Ltd.

629 Beaverdam Road N.E.,
 Calgary Alberta T2K 4W7
 Tel: 274-2777 Fax: 275-0541

TO: 26 BT RESOURCE CO., LTD
 Suite 200, 5920 McLeod Trail S.W.,
 Calgary, Alberta
 T2H 0K2

FILE: 44988

DATE: October 2, 2002

APPENDIX 6 (CONTINUED)

Attn: Sudhir Jain

PGM ANALYSIS

Sample No.	Au ppb	Pd ppb	Pt ppb	Rh ppb
0+00N 37+75S	<5	<5	<5	<5
38+00S	30	<5	<5	<5
38+25S	<5	<5	<5	<5
38+50S	<5	<5	<5	<5
38+75S	485	<5	<5	<5
39+00S	963	<5	<5	<5
39+25S	503	<5	<5	<5
39+50S	430	<5	<5	<5
39+75S	262	<5	<5	<5
40+00S	<5	<5	<5	<5
40+25S	105	<5	<5	<5
40+50S	7	<5	<5	<5
40+75S	<5	<5	<5	<5
41+00S	<5	<5	<5	<5
41+25S	1585	<5	<5	<5
41+50S	297	<5	<5	<5
41+75S	<5	<5	<5	<5
42+00S	<5	<5	<5	<5
42+25S	<5	<5	<5	<5
42+50S	<5	<5	<5	<5
42+75S	<5	<5	<5	<5
43+00S	<5	<5	<5	<5
43+25S	<5	<5	<5	<5
43+50S	<5	<5	<5	<5
43+75S	<5	<5	<5	<5
44+00E	<5	<5	<5	<5
44+25E	<5	<5	<5	<5
44+50E	<5	<5	<5	<5
44+75E	<5	<5	<5	<5
45+00E	<5	<5	<5	<5

Certified by: _____

Loring Laboratories Ltd.

629 Beaverdam Road N.E.,
 Calgary Alberta T2K 4W7
 Tel: 274-2777 Fax: 275-0541

TO: 26 BT RESOURCE CO., LTD
 Suite 200, 5920 McLeod Trail S.W.,
 Calgary, Alberta
 T2H 0K2

FILE: 44988

DATE: October 2, 2002

APPENDIX 6 (CONTINUED)

Attn: Sudhir Jain

PGM ANALYSIS

Sample No.	Au ppb	Pd ppb	Pt ppb	Rh ppb
0+00N 45+25E	<5	5	<5	<5
45+50E	<5	<5	<5	<5
45+75E	<5	<5	<5	<5
46+00E	<5	<5	<5	<5
46+25E	<5	<5	<5	<5
46+50E	<5	<5	<5	<5
46+75E	<5	<5	<5	<5
47+00E	<5	<5	<5	<5
47+25E	<5	<5	<5	<5
47+50E	<5	<5	<5	<5
47+75E	<5	<5	<5	<5
48+00E	<5	<5	<5	<5
48+25E	<5	<5	<5	<5
48+50E	<5	<5	<5	<5
48+75E	<5	<5	<5	<5
49+00E	<5	<5	<5	<5
49+25E	<5	<5	<5	<5
49+50E	<5	<5	<5	<5
49+75E	<5	<5	<5	<5
50+00E	<5	<5	<5	<5
50+25E	153	<5	<5	<5
50+50E	108	<5	<5	<5
50+75E	184	<5	<5	<5
51+00E	72	<5	<5	<5
PGM- Std.(333ppb)	329	325	318	326

Certified by: _____

Loring Laboratories Ltd.

629 Beaverdam Road N.E.,
 Calgary Alberta T2K 4W7
 Tel: 274-2777 Fax: 275-0541

TO: **26 BT RESOURCE CO., LTD**
 Suite 200, 5920 McLeod Trail S.W.,
 Calgary, Alberta
 T2H 0K2

FILE: 44988

DATE: October 2, 2002

APPENDIX 6 (CONTINUED)

Attn: Sudhir Jain

PGM ANALYSIS

Sample No.	Au ppb	Pd ppb	Pt ppb	Rh ppb
3+00S 30+25E	394	140	<5	<5
30+50E	<5	<5	<5	<5
30+75E	23	<5	<5	<5
31+00E	45	<5	<5	<5
31+25E	<5	<5	<5	<5
31+50E	18	<5	<5	<5
31+75E	226	<5	<5	<5
32+00E	138	<5	<5	<5
32+25E	<5	<5	<5	<5
32+50E	<5	<5	<5	<5
32+75E	<5	<5	<5	<5
33+00E	<5	<5	<5	<5
33+25E	<5	<5	<5	<5
33+50E	<5	<5	<5	<5
33+75E	<5	<5	<5	<5
34+00E	<5	<5	<5	<5
34+25E	<5	<5	<5	<5
34+50E	<5	<5	<5	<5
34+75E	<5	<5	<5	<5
35+00E	<5	<5	<5	<5
35+25E	<5	<5	<5	<5
35+50E	<5	<5	<5	<5
35+75E	<5	<5	<5	<5
36+25E	<5	<5	<5	<5
36+50E	<5	<5	<5	<5
36+75E	<5	<5	<5	<5
37+00E	<5	<5	<5	<5
37+25E	<5	<5	<5	<5
37+50E	<5	<5	<5	<5

Certified by: _____

Loring Laboratories Ltd.

629 Beaverdam Road N.E.,
Calgary Alberta T2K 4W7
Tel: 274-2777 Fax: 275-0541

TO: 26 BT RESOURCE CO., LTD
Suite 200, 5920 McLeod Trail S.W.,
Calgary, Alberta
T2H 0K2

FILE: 44988

DATE: October 2, 2002

APPENDIX 6 (CONTINUED)

Attn: Sudhir Jain

PGM ANALYSIS

Sample No.	Au ppb	Pd ppb	Pt ppb	Rh ppb
3+00S 37+75E	<5	<5	<5	<5
38+00E	10	<5	<5	<5
38+25E	<5	<5	<5	<5
38+50E	<5	<5	<5	<5
38+75E	<5	<5	<5	<5
39+00E	<5	<5	<5	<5
39+25E	<5	<5	<5	<5
39+50E	<5	<5	<5	<5
39+75E	<5	<5	<5	<5
40+00E	<5	<5	<5	<5
40+25E	<5	<5	<5	<5
40+50E	25	<5	<5	<5
40+75E	<5	<5	<5	<5
41+00E	10	<5	<5	<5
41+25E	175	<5	<5	<5
41+50E	40	<5	<5	<5
41+75E	84	<5	<5	<5
42+00E	180	<5	<5	<5
42+25E	16	<5	<5	<5
42+50E	<5	<5	<5	<5
42+75E	<5	<5	<5	<5
43+00E	18	<5	<5	<5
43+25E	<5	<5	<5	<5
43+50E	20	<5	<5	<5
43+75E	80	<5	<5	<5
44+00E	145	<5	<5	<5
44+25E	22	<5	<5	<5
44+50E	<5	<5	<5	<5
44+75E	20	<5	<5	<5
45+00E	<5	<5	<5	<5

Certified by: _____

Loring Laboratories Ltd.

629 Beaverdam Road N.E.,
 Calgary Alberta T2K 4W7
 Tel: 274-2777 Fax: 275-0541

TO: 26 BT RESOURCE CO., LTD
 Suite 200, 5920 McLeod Trail S.W.,
 Calgary, Alberta
 T2H 0K2

FILE: 44988

DATE: October 2, 2002

APPENDIX 6 (CONTINUED)

Attn: Sudhir Jain

PGM ANALYSIS

Sample No.	Au ppb	Pd ppb	Pt ppb	Rh ppb
3+00S 45+25E	<5	<5	<5	<5
45+50E	<5	<5	<5	<5
45+75E	80	<5	<5	<5
46+00E	14	<5	<5	<5
46+25E	12	<5	<5	<5
46+50E	<5	<5	<5	<5
46+75E	9	<5	<5	<5
47+00E	<5	<5	<5	<5
47+25E	<5	<5	<5	<5
47+50E	<5	<5	<5	<5
47+75E	<5	<5	<5	<5
48+00E	11	<5	<5	<5
48+25E	7	<5	<5	<5
48+50E	<5	<5	<5	<5
48+75E	7	<5	<5	<5
49+00E	<5	<5	<5	<5
49+25E	<5	<5	<5	<5
49+50E	11	<5	<5	<5
49+75E	12	<5	<5	<5
50+00E	<5	<5	<5	<5
50+25E	<5	<5	<5	<5
50+50E	<5	<5	<5	<5
50+75E	<5	<5	<5	<5
51+00E	<5	<5	<5	<5
PGM- Std.(333ppb)	318	308	322	332

Certified by: _____

Loring Laboratories Ltd.

629 Beaverdam Road N.E.,
Calgary Alberta T2K 4W7
Tel: 274-2777 Fax: 275-0541

TO: **26 BT RESOURCE CO., LTD**
Suite 200, 5920 McLeod Trail S.W.,
Calgary, Alberta
T2H 0K2

FILE: 44988

DATE: October 2, 2002

APPENDIX 6 (CONTINUED)

Attn: Sudhir Jain

PGM ANALYSIS

Sample No.	Au ppb	Pd ppb	Pt ppb	Rh ppb
5+00S 30+25E	<5	<5	<5	<5
30+50E	<5	<5	<5	<5
30+75E	<5	<5	<5	<5
31+00E	38	<5	<5	<5
31+25E	<5	<5	<5	<5
31+50E	<5	<5	<5	<5
31+75E	23	<5	<5	<5
32+00E	51	<5	<5	<5
32+25E	24	<5	<5	<5
32+50E	23	<5	<5	<5
32+75E	20	<5	<5	<5
33+00E	<5	<5	<5	<5
33+25E	<5	<5	<5	<5
33+50E	12	<5	<5	<5
33+75E	55	<5	<5	<5
34+00E	15	<5	<5	<5
34+25E	86	<5	<5	<5
35+00E	<5	<5	<5	<5
35+25E	19	<5	<5	<5
35+50E	<5	<5	<5	<5
35+75E	<5	<5	<5	<5
36+00E	<5	25	<5	<5
36+25E	<5	<5	<5	<5
36+50E	13	<5	<5	<5
36+75E	13	<5	<5	<5
37+00E	22	20	<5	<5
37+25E	6	<5	<5	<5
37+50E	19	<5	<5	<5

Certified by: _____

Loring Laboratories Ltd.

629 Beaverdam Road N.E.,
 Calgary Alberta T2K 4W7
 Tel: 274-2777 Fax: 275-0541

TO: 26 BT RESOURCE CO., LTD
 Suite 200, 5920 McLeod Trail S.W.,
 Calgary, Alberta
 T2H 0K2

FILE: 44988

DATE: October 2, 2002

APPENDIX 6 (CONTINUED)

Attn: Sudhir Jain

PGM ANALYSIS

Sample No.	Au ppb	Pd ppb	Pt ppb	Rh ppb
5+00S 37+75E	14	10	<5	<5
38+00E	9	<5	<5	<5
38+25E	10	<5	<5	<5
38+50E	12	<5	<5	<5
38+75E	12	<5	<5	<5
39+00E	13	22	<5	<5
39+25E	30	<5	<5	<5
39+50E	12	<5	<5	<5
39+75E	13	<5	<5	<5
40+00E	13	42	<5	<5
40+25E	<5	15	<5	<5
40+50E	<5	10	<5	<5
40+75E	21	<5	<5	<5
41+00E	24	5	<5	<5
41+25E	18	10	<5	<5
41+50E	<5	15	<5	<5
41+75E	47	<5	<5	<5
42+00E	9	50	<5	<5
42+25E	<5	15	<5	<5
42+50E	<5	<5	<5	<5
42+75E	<5	20	<5	<5
43+00E	<5	<5	<5	<5
43+25E	<5	20	<5	<5
43+50E	<5	<5	<5	<5
43+75E	<5	<5	<5	<5
44+00E	<5	<5	<5	<5
44+25E	<5	<5	<5	<5
44+50E	<5	10	<5	<5
44+75E	<5	<5	<5	<5
45+00E	<5	<5	<5	<5

Certified by: _____

Loring Laboratories Ltd.

629 Beaverdam Road N.E.,
 Calgary Alberta T2K 4W7
 Tel: 274-2777 Fax: 275-0541

TO: **26 BT RESOURCE CO., LTD**
 Suite 200, 5920 McLeod Trail S.W.,
 Calgary, Alberta
 T2H 0K2

FILE: 44988

DATE: October 2, 2002

APPENDIX 6 (CONTINUED)

Attn: Sudhir Jain

PGM ANALYSIS

Sample No.	Au ppb	Pd ppb	Pt ppb	Rh ppb
5+00S 45+25E	11	<5	<5	<5
45+50E	<5	10	<5	<5
45+75E	<5	22	<5	<5
46+00E	<5	<5	<5	<5
46+25E	<5	<5	<5	<5
46+50E	<5	<5	<5	<5
46+75E	<5	<5	<5	<5
47+00E	10	<5	<5	<5
47+25E	<5	<5	<5	<5
47+50E	<5	<5	<5	<5
47+75E	<5	<5	<5	<5
48+00E	<5	30	<5	<5
48+25E	<5	<5	<5	<5
48+50E	5	<5	<5	<5
48+75E	<5	<5	<5	<5
49+00E	5	<5	<5	<5
49+25E	<5	20	<5	<5
49+50E	<5	<5	<5	<5
49+75E	5	<5	<5	<5
50+00E	45	<5	<5	<5
50+25E	25	15	<5	<5
50+50E	95	10	<5	<5
50+75E	25	<5	<5	<5
51+00E	<5	<5	<5	<5
PGM- Std.(333ppb)	334	325	329	316

Certified by: _____

Loring Laboratories Ltd.

629 Beaverdam Road N.E.,
 Calgary Alberta T2K 4W7
 Tel: 274-2777 Fax: 275-0541

TO: 26 BT RESOURCE CO., LTD
 Suite 200, 5920 McLeod Trail S.W.,
 Calgary, Alberta
 T2H 0K2

FILE: 44988

DATE: October 2, 2002

APPENDIX 6 (CONTINUED)

Attn: Sudhir Jain

PGM ANALYSIS

Sample No.	Au ppb	Pd ppb	Pt ppb	Rh ppb
34+00E 0+25N	30	<5	<5	<5
0+50N	<5	<5	<5	<5
0+75N	25	<5	<5	<5
1+00N	<5	<5	<5	<5
1+25N	45	<5	<5	<5
1+50N	<5	<5	<5	<5
1+75N	<5	<5	<5	<5
2+00N	<5	<5	<5	<5
2+25N	<5	<5	<5	<5
2+50N	<5	<5	<5	<5
2+75N	<5	<5	<5	<5
3+00N	<5	<5	<5	<5
3+25N	<5	<5	<5	<5
3+50N	<5	<5	<5	<5
3+75N	<5	<5	<5	<5
4+00N	35	<5	<5	<5
4+25N	<5	<5	<5	<5
4+50N	<5	<5	<5	<5
4+75N	16	<5	<5	<5
5+00N	<5	<5	<5	<5
5+25N	17	<5	<5	<5
5+50N	<5	<5	<5	<5
5+75N	20	<5	<5	<5
6+00N	<5	<5	<5	<5
6+25N	<5	<5	<5	<5
6+50N	<5	<5	<5	<5
6+75N	<5	<5	<5	<5
7+00N	<5	<5	<5	<5
7+25N	<5	<5	<5	<5
7+50N	<5	<5	<5	<5

Certified by: _____

Loring Laboratories Ltd.

629 Beaverdam Road N.E.,
 Calgary Alberta T2K 4W7
 Tel: 274-2777 Fax: 275-0541

TO: 26 BT RESOURCE CO., LTD
 Suite 200, 5920 McLeod Trail S.W.,
 Calgary, Alberta
 T2H 0K2

FILE: 44988

DATE: October 2, 2002

APPENDIX 6 (CONTINUED)

Attn: Sudhir Jain

PGM ANALYSIS

Sample No.	Au ppb	Pd ppb	Pt ppb	Rh ppb
34+00E 7+75N	<5	<5	<5	<5
8+00N	<5	<5	<5	<5
8+25N	5	<5	<5	<5
8+50N	<5	<5	<5	<5
8+75N	<5	<5	<5	<5
9+00N	<5	<5	<5	<5
9+25N	<5	<5	<5	<5
9+50N	<5	<5	<5	<5
9+75N	<5	<5	<5	<5
10+00N	<5	20	<5	<5
10+25N	<5	<5	<5	<5
10+50N	<5	<5	<5	<5
10+75N	<5	<5	<5	<5
11+00N	<5	<5	<5	<5
11+25N	<5	<5	<5	<5
11+50N	<5	<5	<5	<5
11+75N	<5	<5	<5	<5
12+00N	<5	<5	<5	<5
12+25N	<5	<5	<5	<5
12+50N	<5	<5	<5	<5
12+75N	190	20	<5	<5
13+00N	25	<5	<5	<5
13+25N	<5	<5	<5	<5
13+50N	<5	<5	<5	<5
13+75N	<5	<5	<5	<5
14+00N	<5	<5	<5	<5
14+25N	<5	<5	<5	<5
14+75N	<5	<5	<5	<5
14+75N	<5	<5	<5	<5
15+00N	5	<5	<5	<5

Certified by: _____

Loring Laboratories Ltd.

629 Beaverdam Road N.E.,
Calgary Alberta T2K 4W7
Tel: 274-2777 Fax: 275-0541

TO: **26 BT RESOURCE CO., LTD**
Suite 200, 5920 McLeod Trail S.W.,
Calgary, Alberta
T2H 0K2

FILE: 44988

DATE: October 2, 2002

APPENDIX 6 (CONTINUED)

Attn: Sudhir Jain

PGM ANALYSIS

Sample No.	Au ppb	Pd ppb	Pt ppb	Rh ppb
34+00E 15+25N	10	<5	<5	<5
15+50N	5	<5	<5	<5
15+75N	13	<5	<5	<5
16+00N	19	<5	<5	<5
41+00E 0+25N	9	<5	<5	<5
0+50N	16	<5	<5	<5
0+75N	70	<5	<5	<5
0+25S	15	<5	<5	<5
0+50S	<5	<5	<5	<5
0+75S	15	<5	<5	<5
1+00N	<5	<5	<5	<5
1+25N	<5	<5	<5	<5
1+50N	19	<5	<5	<5
1+75N	<5	<5	<5	<5
1+00S	12	<5	<5	<5
1+25S	<5	<5	<5	<5
1+50S	5	<5	<5	<5
1+75S	<5	<5	<5	<5
2+00N	<5	<5	<5	<5
2+25N	<5	<5	<5	<5
2+50N	<5	17	<5	<5
2+75N	<5	57	<5	<5
2+00S	<5	<5	<5	<5
2+25S	<5	<5	<5	<5
2+75S	<5	<5	<5	<5
3+00N	<5	<5	<5	<5
3+00S	<5	<5	<5	<5
3+25S	<5	<5	<5	<5
3+50S	<5	<5	<5	<5
3+75S	<5	<5	<5	<5

Certified by: _____

Loring Laboratories Ltd.

629 Beaverdam Road N.E.,
 Calgary Alberta T2K 4W7
 Tel: 274-2777 Fax: 275-0541

TO: 26 BT RESOURCE CO., LTD
 Suite 200, 5920 McLeod Trail S.W.,
 Calgary, Alberta
 T2H 0K2

FILE: 44988

DATE: October 2, 2002

Attn: Sudhir Jain

APPENDIX 6 (CONTINUED)

PGM ANALYSIS

Sample No.	Au ppb	Pd ppb	Pt ppb	Rh ppb
47+00E 0+25N	<5	<5	<5	<5
0+50N	<5	<5	<5	<5
0+75N	<5	<5	<5	<5
0+25S	10	<5	<5	<5
0+50S	14	<5	<5	<5
0+75S	5	<5	<5	<5
1+00N	<5	<5	<5	<5
1+00S	<5	<5	<5	<5
1+25S	<5	<5	<5	<5
1+50S	<5	<5	<5	<5
1+75S	<5	<5	<5	<5
2+00S	10	<5	<5	<5
2+25S	5	<5	<5	<5
2+50S	<5	<5	<5	<5
2+75S	7	<5	<5	<5
3+00S	<5	<5	<5	<5
3+25S	6	<5	<5	<5
3+50S	<5	<5	<5	<5
3+75S	<5	<5	<5	<5
4+00S	<5	5	<5	<5
S-200Z-1	55	5	<5	<5
PGM- Std.(333ppb)	334	338	328	329

Certified by: _____

Loring Laboratories Ltd.

629 Beaverdam Road N.E.,
 Calgary Alberta T2K 4W7
 Tel: 274-2777 Fax: 275-0541

TO: 26 BT RESOURCE CO., LTD
 Suite 200, 5920 McLeod Trail S.W.,
 Calgary, Alberta
 T2H 0K2

FILE: 44988

DATE: October 2, 2002

APPENDIX 6 (CONTINUED)

Attn: Sudhir Jain

PGM ANALYSIS

Sample No.	Au ppb	Pd ppb	Pt ppb	Rh ppb
41+00E 4+00S	<5	<5	<5	<5
4+25S	<5	<5	<5	<5
4+50S	10	<5	<5	<5
4+75S	5	<5	<5	<5
5+00S	5	<5	<5	<5
43+00E 0+25N	<5	<5	<5	<5
0+50N	10	<5	<5	<5
0+75N	5	<5	<5	<5
0+25S	5	<5	<5	<5
0+50S	6	<5	<5	<5
0+75S	7	<5	<5	<5
1+00N	5	<5	<5	<5
1+00S	5	<5	<5	<5
1+25S	<5	<5	<5	<5
1+50S	<5	<5	<5	<5
1+75S	<5	<5	<5	<5
2+25S	<5	<5	<5	<5
2+50S	<5	<5	<5	<5
2+75S	<5	<5	<5	<5
3+00S	<5	<5	<5	<5
3+25S	15	<5	<5	<5
3+50S	<5	<5	<5	<5
4+00S	12	<5	<5	<5
4+25S	<5	<5	<5	<5
4+50S	<5	<5	<5	<5
4+75S	<5	<5	<5	<5
5+00S	5	<5	<5	<5
5+25S	<5	<5	<5	<5
5+50S	9	<5	<5	<5
5+75S	<5	<5	<5	<5

Certified by: _____

Loring Laboratories Ltd.

629 Beaverdam Road N.E.,
 Calgary Alberta T2K 4W7
 Tel: 274-2777 Fax: 275-0541

TO: 26 BT RESOURCE CO., LTD
 Suite 200, 5920 McLeod Trail S.W.,
 Calgary, Alberta
 T2H 0K2

FILE: 44988

DATE: October 2, 2002

APPENDIX 6 (CONTINUED)

Attn: Sudhir Jain

PGM ANALYSIS

Sample No.	Au ppb	Pd ppb	Pt ppb	Rh ppb
43+00E 6+00S	<5	<5	<5	<5
45+00E 0+25N	10	<5	<5	<5
0+50N	<5	25	<5	<5
0+75N	<5	<5	<5	<5
0+00S	<5	<5	<5	<5
0+25S	<5	<5	<5	<5
0+75S	<5	<5	<5	<5
1+00N	<5	<5	<5	<5
1+00S	<5	<5	<5	<5
1+25S	5	<5	<5	<5
1+50S	5	<5	<5	<5
1+75S	<5	<5	<5	<5
2+00S	<5	<5	<5	<5
2+25S	10	<5	<5	<5
2+50S	35	<5	<5	<5
2+75S	15	10	<5	<5
3+25S	10	<5	<5	<5
3+50S	10	<5	<5	<5
3+75S	<5	<5	<5	<5
4+00S	5	<5	<5	<5
4+25S	15	<5	<5	<5
4+50S	<5	<5	<5	<5
4+75S	10	<5	<5	<5
5+25S	15	<5	<5	<5
5+50S	15	<5	<5	<5
5+75S	<5	<5	<5	<5
6+00S	<5	<5	<5	<5
PGM- Std.(333ppb)	308	322	319	309

Certified by: _____

Loring Laboratories Ltd.

629 Beaverdam Road N.E.,
 Calgary Alberta T2K 4W7
 Tel: 274-2777 Fax: 275-0541

TO: 26 BT RESOURCE CO., LTD
 Suite 200, 5920 McLeod Trail S.W.,
 Calgary, Alberta
 T2H 0K2

FILE: 45071

DATE: October 29, 2002

APPENDIX 6 (CONTINUED)

Attn: Sudhir Jain

PGM ANALYSIS

Sample No.	Au ppb	Pd ppb	Pt ppb	Rh ppb
STN 0+00 LINE27+00E	<5	<5	<5	<5
LINE 0+00 27+00E	<5	<5	<5	<5
LINE 0+00 27+25E	<5	<5	<5	<5
LINE 0+00 27+50E	<5	<5	<5	<5
LINE 0+00 27+75E	<5	15	<5	<5
LINE 0+00 28+00E	<5	<5	<5	<5
LINE 0+00 28+25E	<5	<5	<5	<5
LINE 0+00 28+50E	<5	<5	<5	<5
LINE 0+00 28+75E	<5	<5	<5	<5
LINE 0+00 29+00E	<5	<5	<5	<5
LINE 0+00 29+25E	<5	<5	<5	<5
LINE 0+00 29+50E	<5	<5	<5	<5
LINE 0+00 29+75E	<5	<5	<5	<5
27+00E 0+25S	75	<5	<5	<5
27+00E 0+25N	<5	<5	<5	<5
27+00E 0+50N	20	<5	<5	<5
27+00E 0+50S	75	<5	<5	<5
27+00E 0+75N	85	<5	<5	<5
27+00E 0+75S	150	<5	<5	<5
27+00E 1+00N	45	<5	<5	<5
27+00E 1+00S	135	<5	<5	<5
27+00E 1+25N	280	<5	<5	<5
27+00E 1+25S	80	<5	<5	<5
27+00E 1+50N	20	<5	<5	<5
27+00E 1+50S	15	<5	<5	<5
27+00E 1+75N	<5	<5	<5	<5
27+00E 1+75S	15	<5	<5	<5
27+00E 2+00N	<5	<5	<5	<5
27+00E 2+00S	<5	<5	<5	<5
27+00E 2+25N	<5	<5	<5	<5

Certified by: _____

Loring Laboratories Ltd.

629 Beaverdam Road N.E.,
 Calgary Alberta T2K 4W7
 Tel: 274-2777 Fax: 275-0541

TO: **26 BT RESOURCE CO., LTD**
 Suite 200, 5920 McLeod Trail S.W.,
 Calgary, Alberta
 T2H 0K2

FILE: 45071

DATE: October 29, 2002

APPENDIX 6 (CONTINUED)

Attn: Sudhir Jain

PGM ANALYSIS

Sample No.	Au ppb	Pd ppb	Pt ppb	Rh ppb
27+00E 2+25S	<5	<5	<5	<5
27+00E 2+50N	5	<5	<5	<5
27+00E 2+50S	<5	<5	<5	<5
27+00E 2+75N	<5	<5	<5	<5
27+00E 2+75S	<5	<5	<5	<5
27+00E 3+00N	<5	<5	<5	<5
27+00E 3+00S	40	<5	<5	<5
STN.3+00S L 27+00E	150	<5	<5	<5
STN.3+00S L27+25E	65	<5	<5	<5
STN.3+00S L27+50E	15	<5	<5	<5
STN.3+00S L27+75E	180	<5	<5	<5
STN.3+00S L28+00E	70	<5	9	<5
STN.3+00S L28+25E	60	<5	<5	<5
STN.3+00S L28+50E	65	<5	<5	<5
STN.3+00S L28+75E	110	<5	<5	<5
STN.3+00S L29+00E	120	<5	<5	<5
STN.3+00S L29+25E	<5	<5	<5	<5
STN.3+00S L29+50E	<5	<5	<5	<5
STN.3+00S L29+75E	<5	<5	<5	<5
27+00E 3+25N	<5	<5	<5	<5
27+00E 3+25S	<5	<5	<5	<5
27+00E 3+50N	<5	<5	<5	<5
27+00E 3+50S	<5	<5	<5	<5
27+00E 3+75N	<5	<5	<5	<5
27+00E 3+75S	<5	<5	<5	<5
27+00E 4+00N	<5	<5	<5	<5
27+00E 4+00S	<5	<5	<5	<5
27+00E 4+25N	<5	<5	<5	<5
27+00E 4+25S	<5	<5	<5	<5
27+00E 4+50N	<5	<5	<5	<5

Certified by: _____

Loring Laboratories Ltd.

629 Beaverdam Road N.E.,
 Calgary Alberta T2K 4W7
 Tel: 274-2777 Fax: 275-0541

TO: **26 BT RESOURCE CO., LTD**
 Suite 200, 5920 McLeod Trail S.W.,
 Calgary, Alberta
 T2H 0K2

FILE: 45071

DATE: October 29, 2002

APPENDIX 6 (CONTINUED)

Attn: Sudhir Jain

PGM ANALYSIS

Sample No.	Au ppb	Pd ppb	Pt ppb	Rh ppb
27+00E 4+50S	<5	<5	<5	<5
27+00E 4+75N	<5	<5	<5	<5
27+00E 4+75S	<5	<5	<5	<5
27+00E 5+00N	<5	<5	<5	<5
27+00E 5+25N	<5	<5	<5	<5
27+00E 5+50N	<5	<5	<5	<5
27+00E 5+75N	<5	<5	<5	<5
27+00E 5+00S	<5	<5	<5	<5
5+00S 27+25E	<5	<5	<5	<5
5+00S 27+50E	<5	<5	<5	<5
5+00S 27+75E	<5	<5	<5	<5
5+00S 28+00E	<5	<5	<5	<5
5+00S 28+25E	<5	<5	<5	<5
5+00S 28+50E	<5	<5	<5	<5
5+00S 28+75E	<5	<5	<5	<5
5+00S 29+00E	<5	<5	<5	<5
5+00S 29+25E	<5	<5	<5	<5
5+00S 29+50E	40	<5	<5	<5
5+00S 29+75E	<5	<5	<5	<5
27+00E 6+00N	<5	30	<5	<5
27+00E 6+25N	<5	<5	<5	<5
27+00E 6+50N	<5	<5	<5	<5
27+00E 6+75N	<5	<5	<5	<5
27+00E 7+00N	<5	<5	<5	<5
27+00E 7+25N	75	<5	<5	<5
27+00E 7+50N	15	<5	<5	<5
27+00E 7+75N	30	<5	<5	<5
27+00E 8+00N	<5	<5	<5	<5
27+00E 8+25N	15	<5	<5	<5
27+00E 8+50N	15	<5	<5	<5

Certified by: _____

Loring Laboratories Ltd.

629 Beaverdam Road N.E.,
 Calgary Alberta T2K 4W7
 Tel: 274-2777 Fax: 275-0541

TO: **26 BT RESOURCE CO., LTD**
 Suite 200, 5920 McLeod Trail S.W.,
 Calgary, Alberta
 T2H 0K2

FILE: 45071

DATE: October 29, 2002

APPENDIX 6 (CONTINUED)

Attn: Sudhir Jain

PGM ANALYSIS

Sample No.	Au ppb	Pd ppb	Pt ppb	Rh ppb
27+00E 8+75N	10	<5	<5	<5
27+00E 9+00N	30	<5	<5	<5
27+00E 9+25N	5	<5	<5	<5
27+00E 9+50N	<5	<5	<5	<5
27+00E 9+75N	<5	<5	<5	<5
27+00E 10+00N	<5	<5	<5	<5
27+00E 10+25N	<5	<5	<5	<5
27+00E 10+50N	15	<5	<5	<5
27+00E 10+75N	35	<5	<5	<5
27+00E 11+00N	<5	<5	<5	<5
27+00E 11+25N	<5	<5	<5	<5
27+00E 11+50N	<5	<5	<5	<5
27+00E 11+75N	<5	<5	<5	<5
27+00E 12+00N	<5	<5	<5	<5
12+00N 27+25E	<5	<5	<5	<5
12+00N 27+50E	<5	<5	<5	<5
12+00N 27+75E	<5	<5	<5	<5
12+25N 27+00E	<5	<5	<5	<5
12+50N 27+00E	<5	<5	<5	<5
12+75N 27+00E	<5	<5	<5	<5
12+00N 28+00E	<5	<5	<5	<5
12+00N 28+25E	<5	<5	<5	<5
12+00N 28+50E	<5	<5	<5	<5
12+00N 28+75E	<5	<5	<5	<5
12+00N 29+00E	<5	<5	<5	<5
12+00N 29+25E	<5	<5	<5	<5
12+00N 29+50E	<5	<5	<5	<5
12+00N 29+75E	<5	<5	<5	<5
12+00N 30+00E	<5	<5	<5	<5
12+00N 30+25E	15	<5	<5	<5

Certified by: _____

Loring Laboratories Ltd.

629 Beaverdam Road N.E.,
 Calgary Alberta T2K 4W7
 Tel: 274-2777 Fax: 276-0541

TO: 26 BT RESOURCE CO., LTD
 Suite 200, 5920 McLeod Trail S.W.,
 Calgary, Alberta
 T2H 0K2

FILE: 45071

DATE: October 29, 2002

APPENDIX 6 (CONTINUED)

Attn: Sudhir Jain

PGM ANALYSIS

Sample No.	Au ppb	Pd ppb	Pt ppb	Rh ppb
12+00N 30+50E	<5	<5	<5	<5
12+00N 30+75E	<5	<5	<5	<5
12+00N 31+00E	<5	<5	<5	<5
12+00N 31+25E	<5	<5	<5	<5
12+00N 31+50E	<5	<5	<5	<5
12+00N 32+25E	<5	<5	<5	<5
12+00N 32+50E	<5	<5	<5	<5
12+00N 33+00E	<5	<5	<5	<5
12+00N 33+25E	<5	<5	<5	<5
12+00N 33+75E	<5	<5	<5	<5
12+00N 34+00E	20	<5	<5	<5
27+00E 13+00N	10	<5	<5	<5
27+00E 13+25N	15	<5	<5	<5
27+00E 13+50N	<5	<5	<5	<5
27+00E 13+75N	10	<5	<5	<5
27+00E 14+00N	8	<5	<5	<5
27+00E 14+25N	100	<5	<5	<5
27+00E 14+50N	<5	<5	<5	<5
PGM- Std.(333ppb)	329	291	308	321

Certified by: _____

STATEMENT OF COSTS

(October 3, 2001 to October 2, 2002)
BT 1 - 6 & 8

A. EXPLORATION COSTS

- Geological Field Trip	
October 3-4/01	\$ 204.68
August 1-6/02	8,435.45
September 30 - Oct. 2/02	1,635.26
- Calculating locations & producing maps	<u>3,200.00</u>

TOTAL EXPLORATION EXPENSES **\$13,475.39**

B. SAMPLE ANALYSIS

- Loring Laboratories Ltd.	<u>\$17,139.02</u>
----------------------------	--------------------

TOTAL SAMPLE ANALYSIS EXPENSES **\$17,139.02**

TOTAL EXPENSES **\$30,614.41**

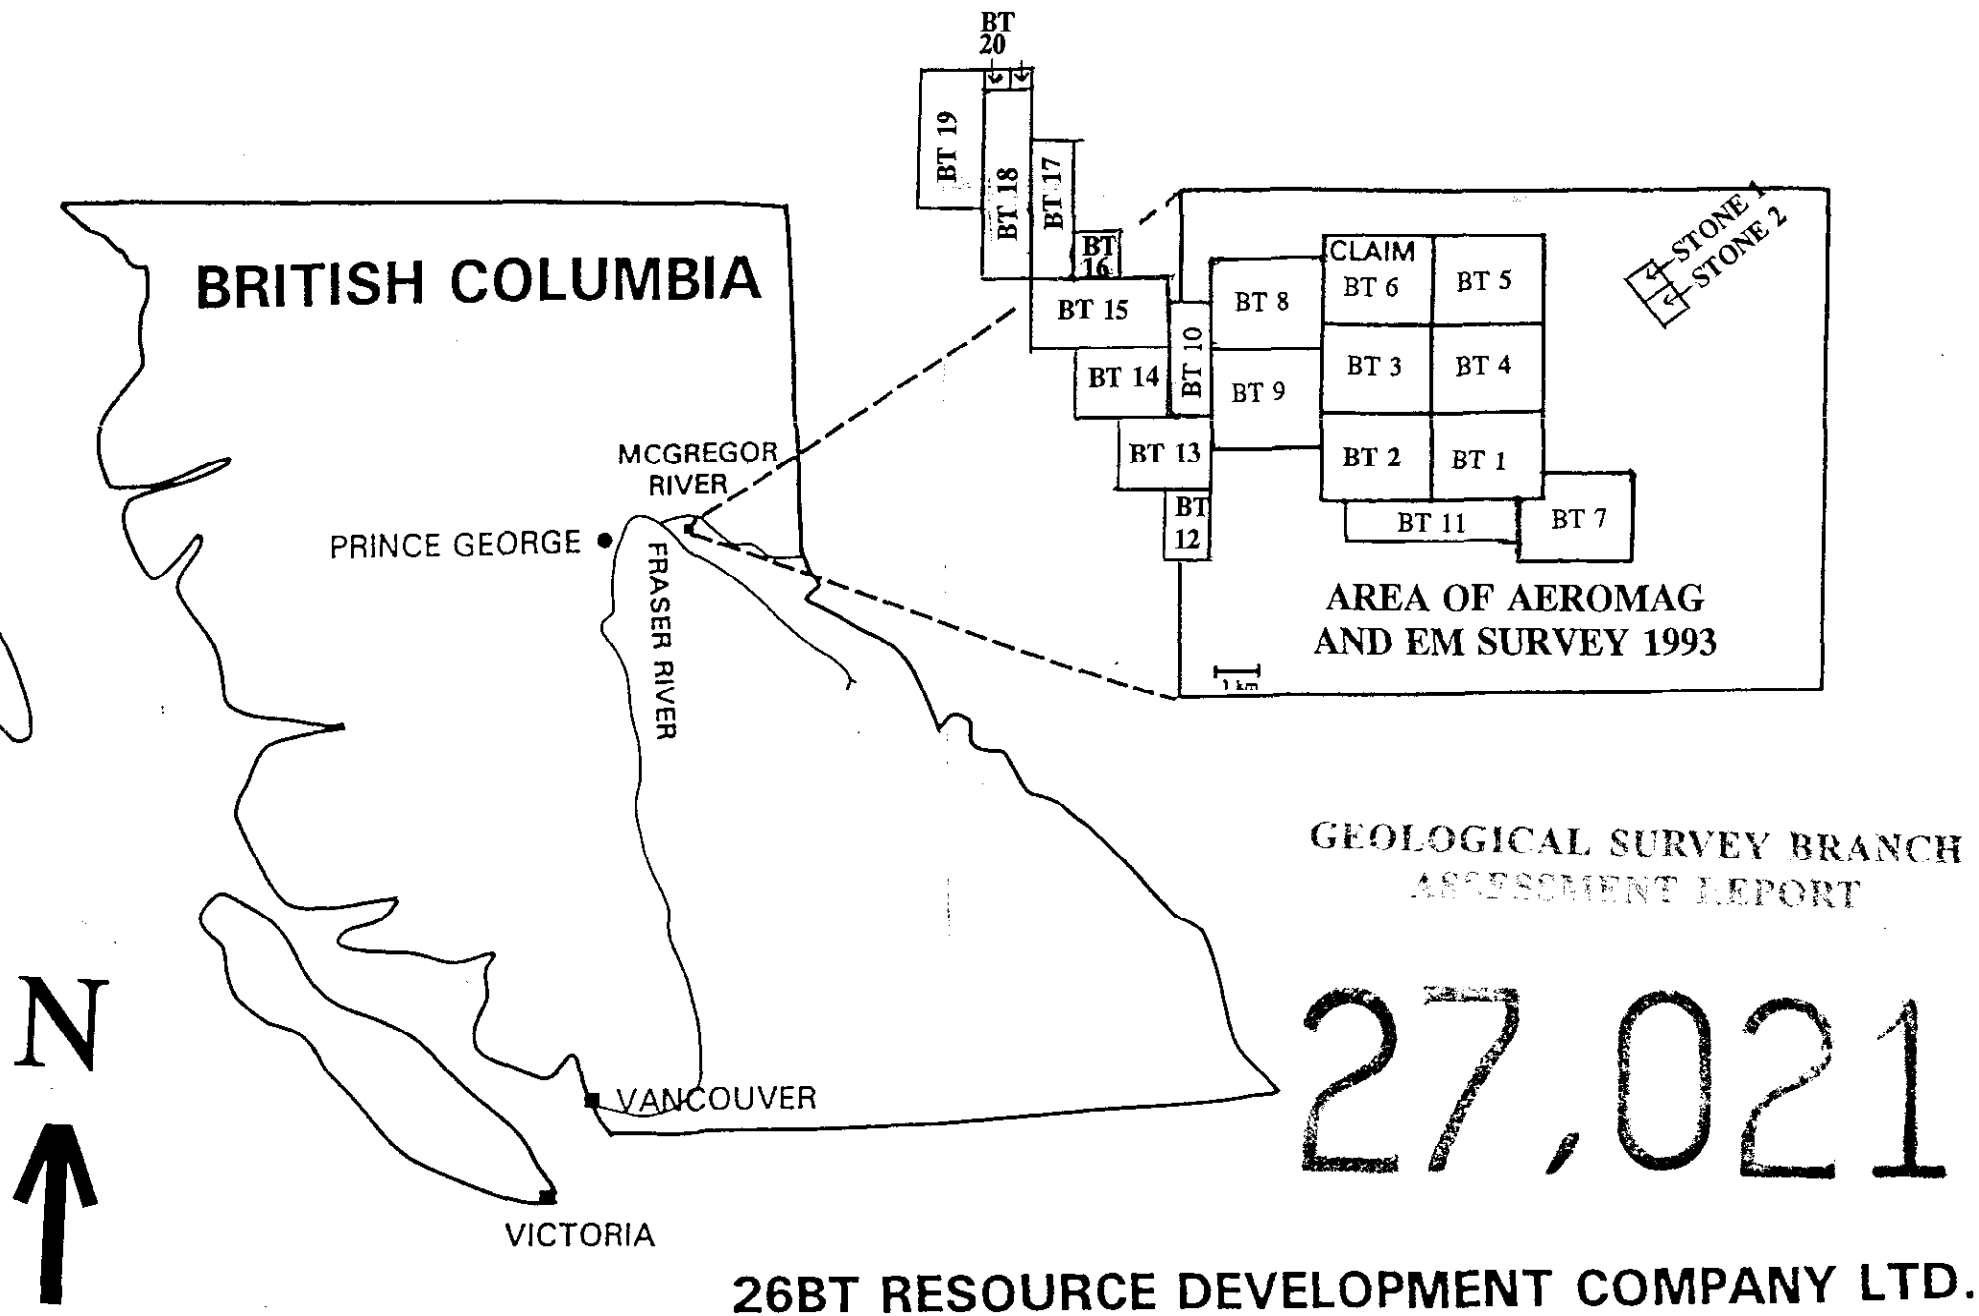
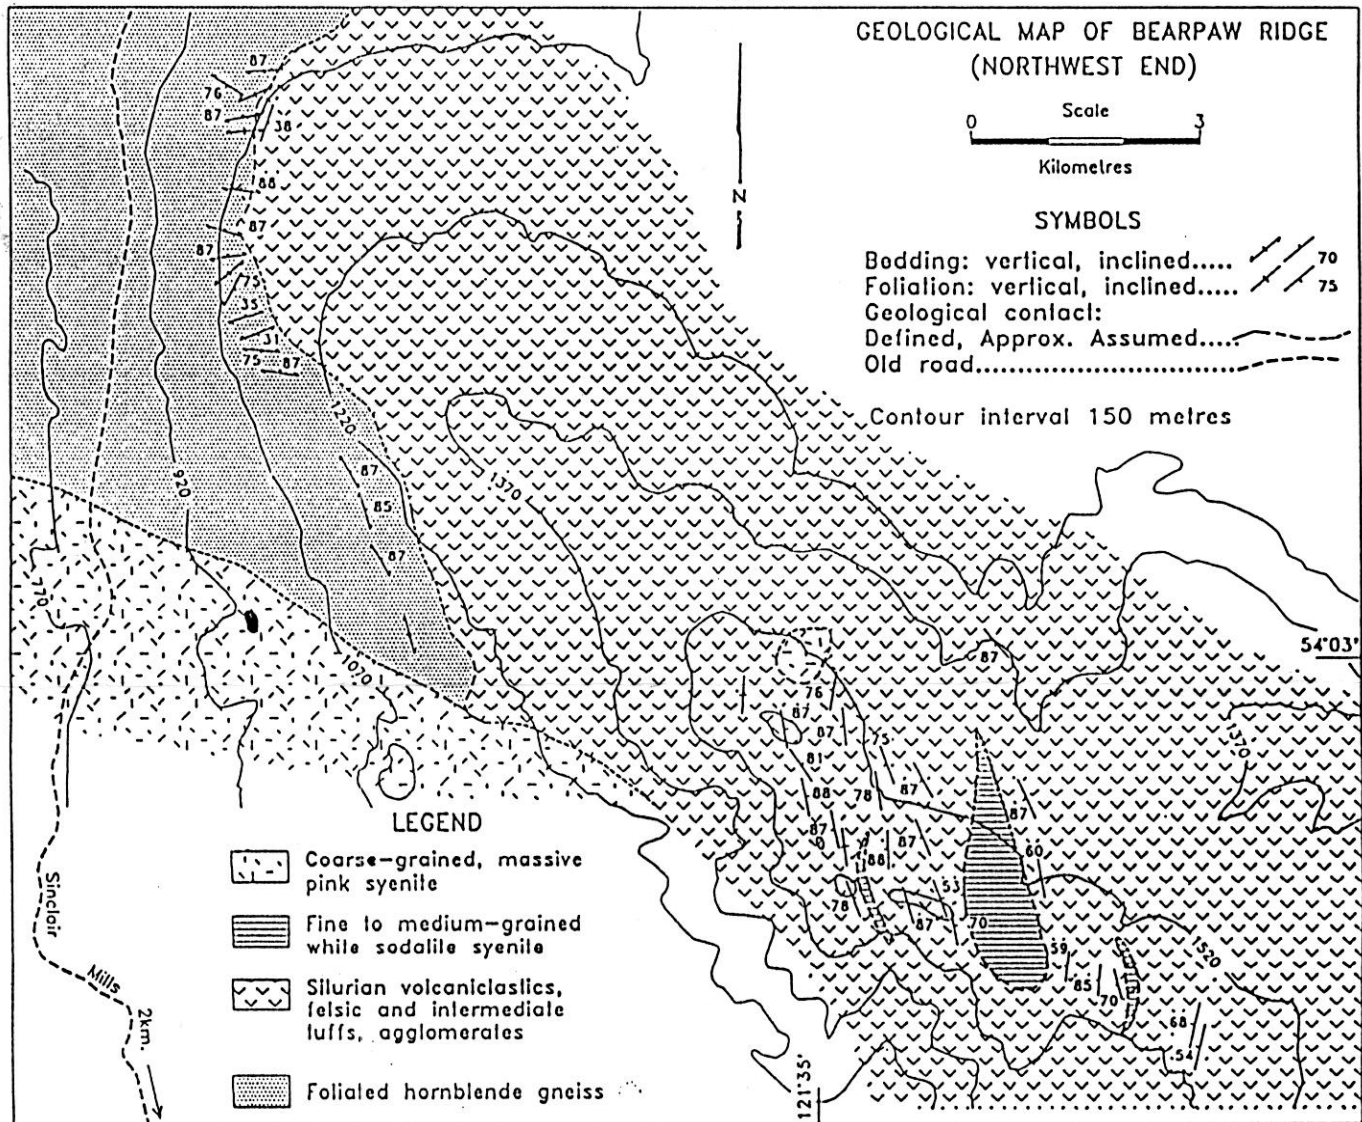


FIGURE 1
AREA OF AEROMAG AND EM SURVEY 1993


CALGARY ALBERTA



**FIGURE 2
GEOLOGICAL MAP OF BEARPAW RIDGE**

GEOLOGICAL SURVEY BRANCH
ASSESSMENT REPORT

27,021

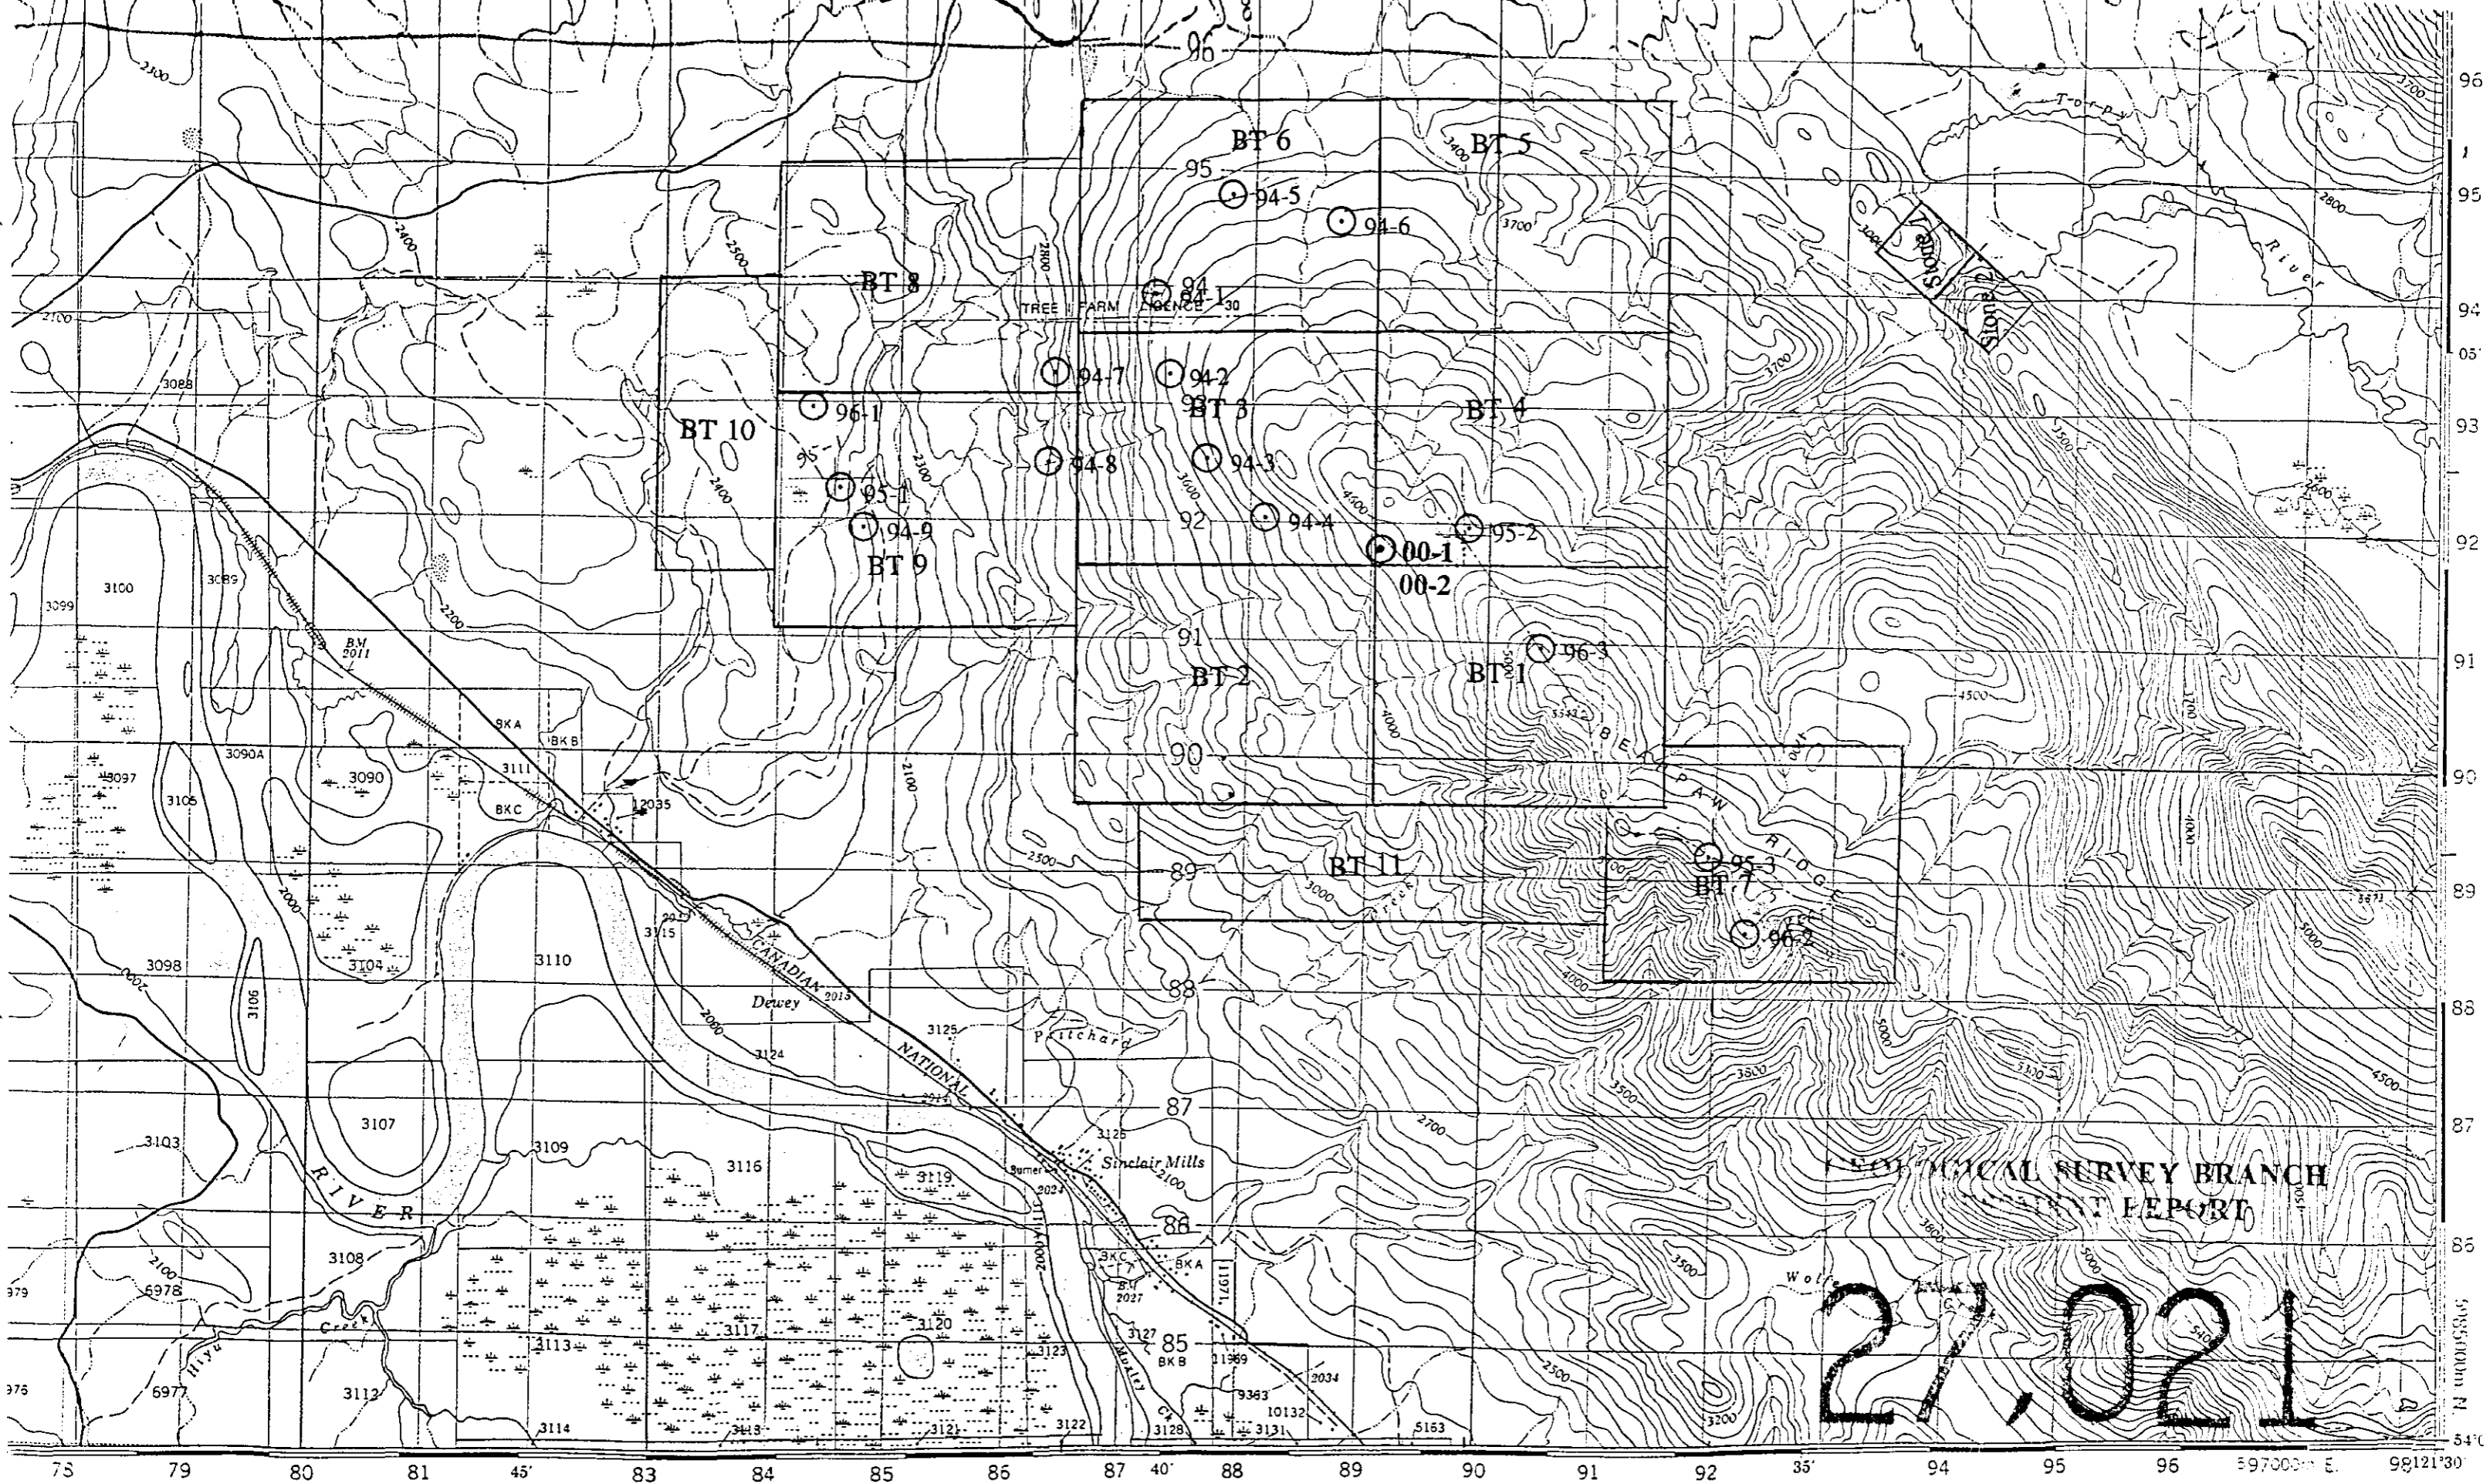

SINCLAIR MILLS
 CARIBOO LAND DISTRICT
 BRITISH COLUMBIA


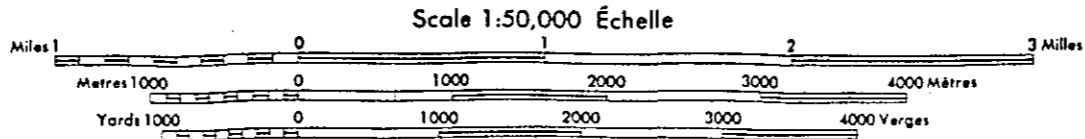


FIGURE 3
LOCATION OF HOLES DRILLED


27,021

①

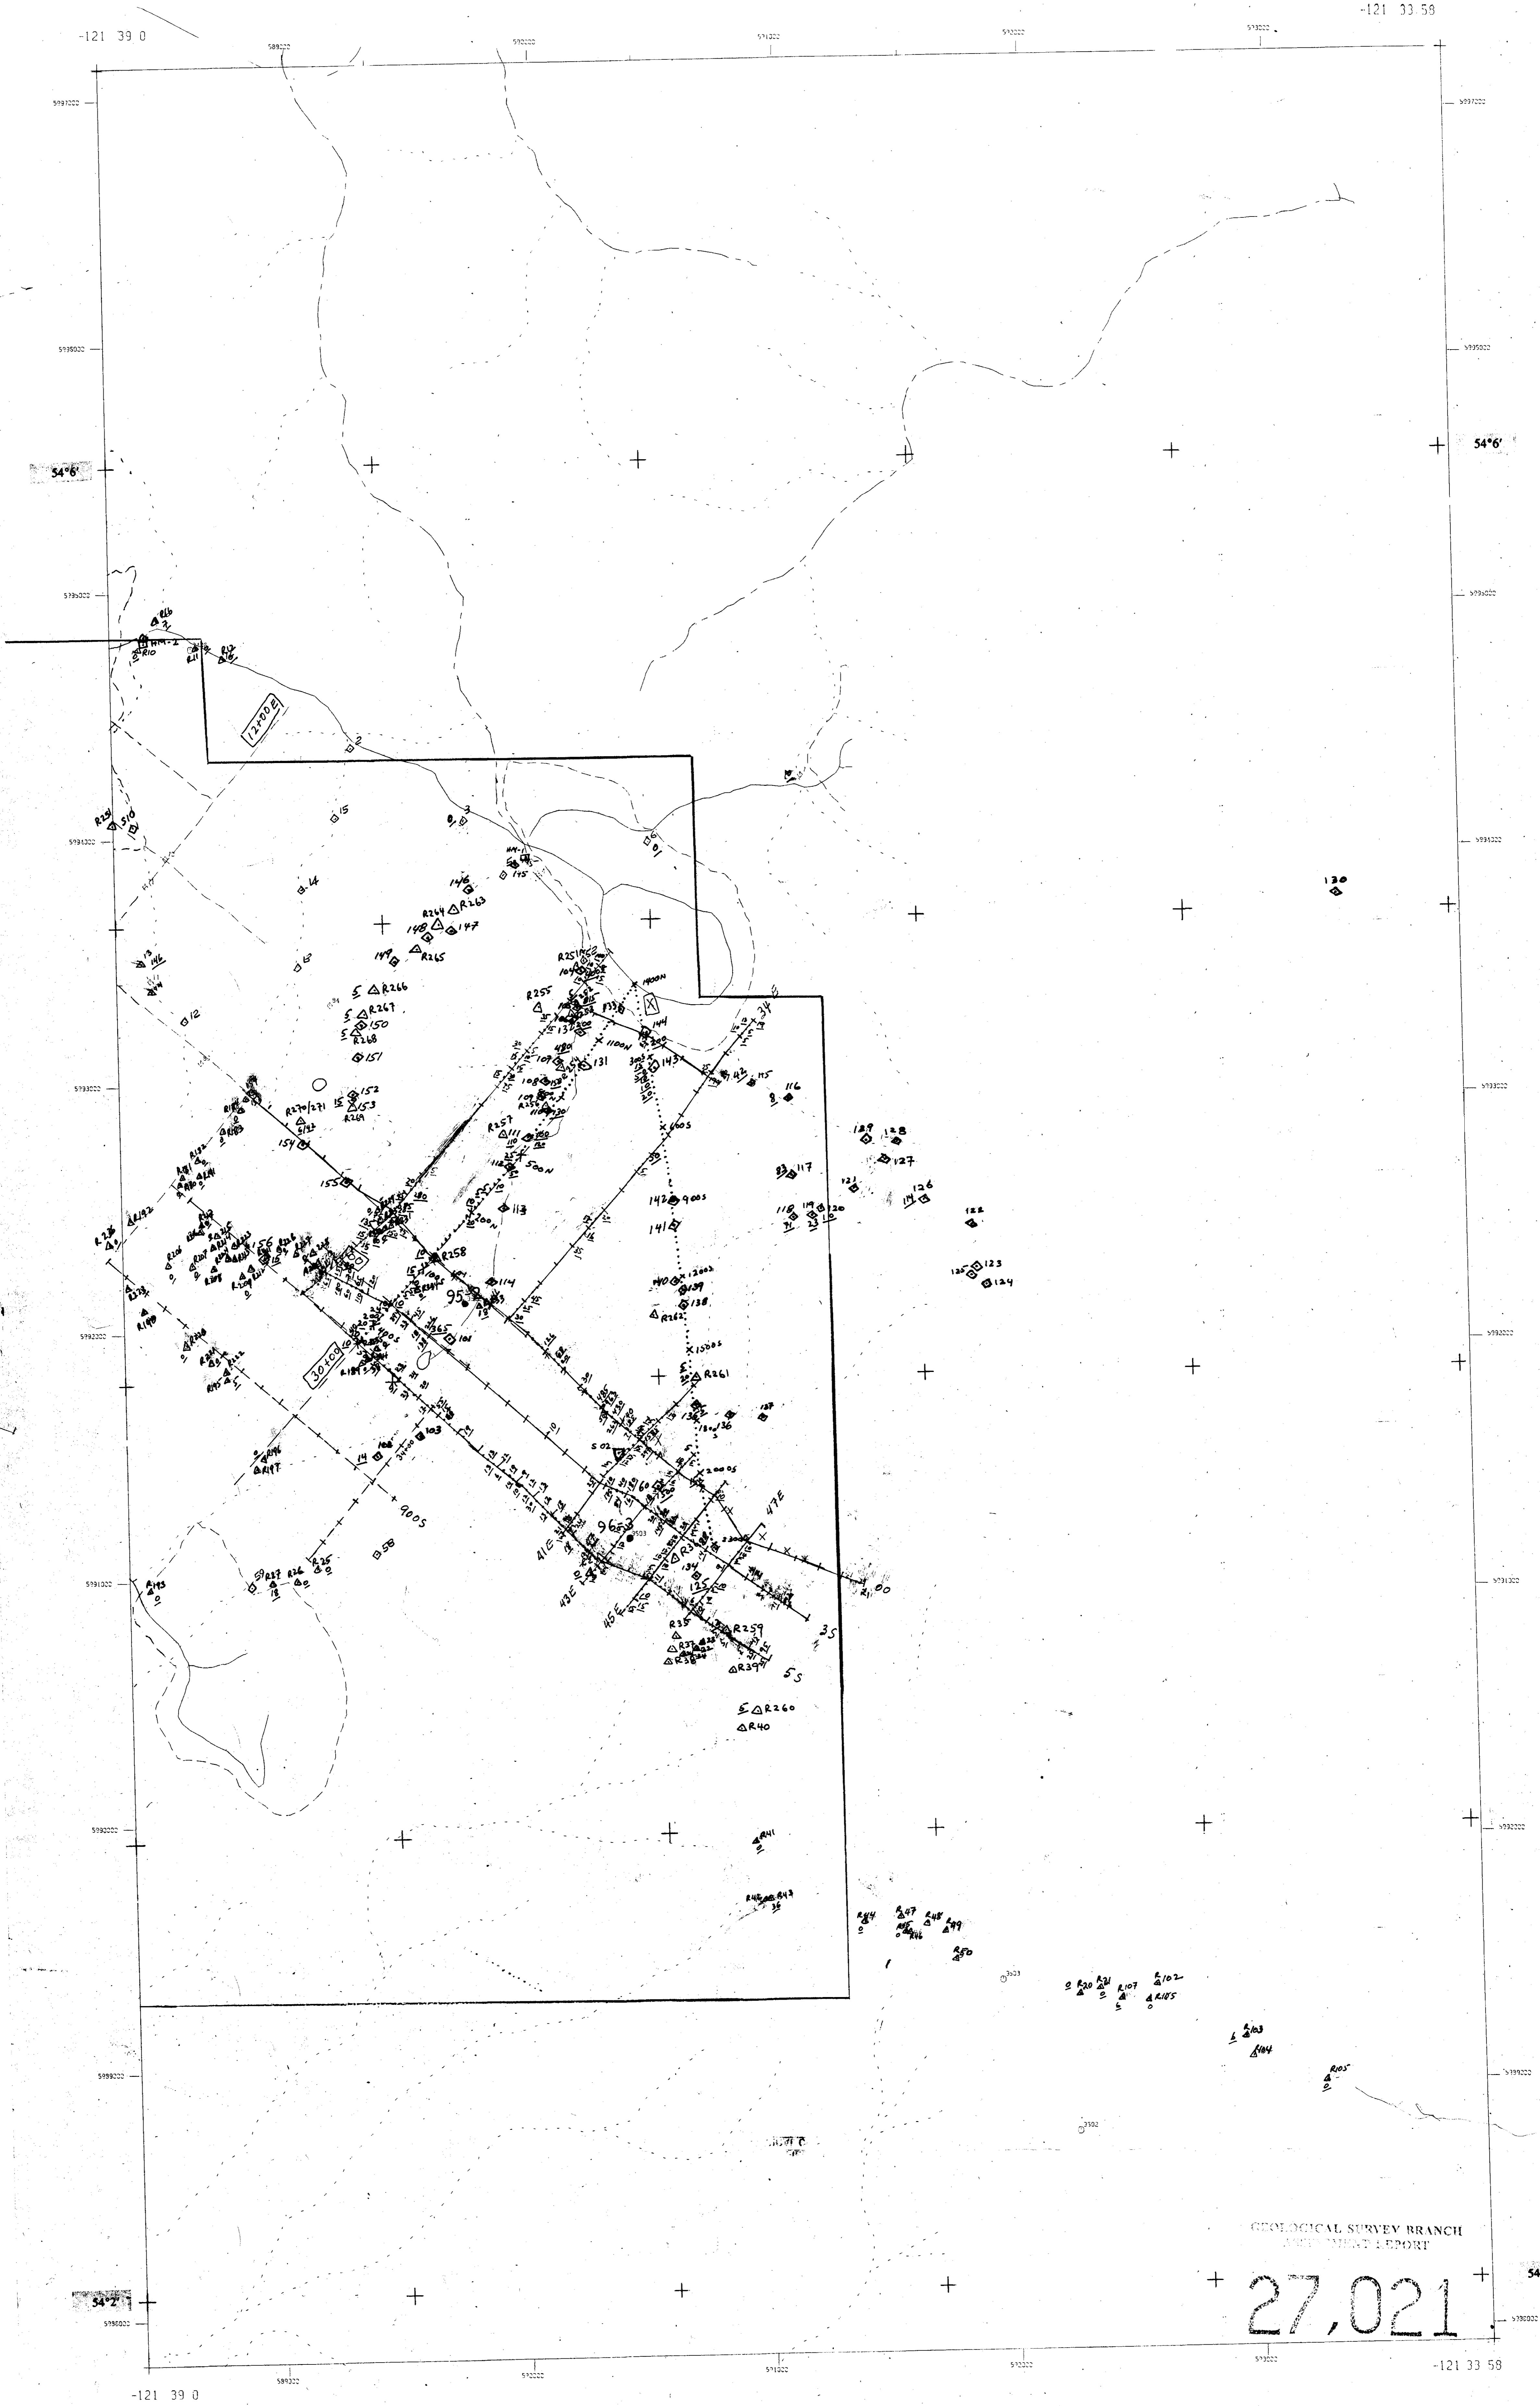

AU content in ppb from silt, soil and rock samples

- △ Rock Samples
- ◇ Silt Sample
- ...x...x Soil Stations
- 27 Au ppb

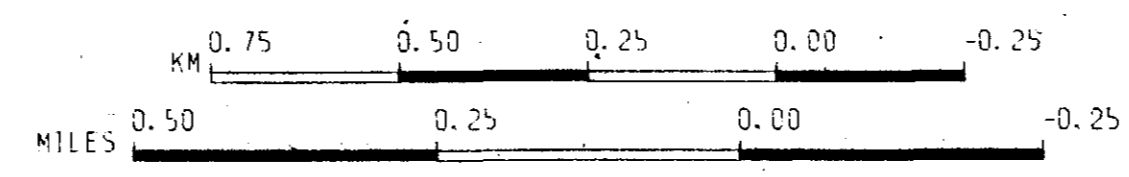

26BT SILT Samples
NAD-83 East

FIGURE 4

SCALE 1:10 000

27,021