

RECEIVED

SEP 13 2005

Gold Commissioner's Office
VANCOUVER, B.C.

**2005
Assessment Report**

**Geological, Geochemical
& Diamond Drilling Report**

on the

Gold Creek Property
(GOLDCREEK, GOLDCREEK2, GOLDCREEK3)
Kamloops Mining Division

N.T.S. 82M/6W
Latitude 51° 20' N
Longitude 119° 59' W

Owner/Operator:

Navasota Resources Ltd.
Suite 626 – 235 First Avenue
Kamloops, B.C., V2C 3J4

GEOLOGICAL SURVEY BRANCH
ASSESSMENT REPORT

27,890

Christopher J. Wild, P. Eng.
Wildrock Resources Consulting & Drafting
September 12, 2005

Table of Contents

1.0	Summary	1
2.0	Introduction.....	2
	2.1 Terms of Reference	
	2.2 Property Description, Location, and Access	
	2.3 Climate and Physiography	
	2.4 Property History	
	2.5 2004-05 Program	
3.0	Geological Setting	6
	3.1 Regional Geology	
	3.2 Property Geology	
	3.2.1 Lithology	
	3.2.2 Structure and Mineralization	
4.0	Soil and Rock Geochemistry.....	8
5.0	Diamond Drilling	9
	5.1 Slate Creek Area	
	5.2 Central Area	
	5.3 Enargite Showing	
6.0	Conclusions and Recommendations	10
7.0	References.....	11

List of Tables

Table 1	Gold Creek Property Mineral Claims.....	2
Table 2	Significant Rock Sample Results	6
Table 3	Summary of Diamond Drill Holes	9
Table 4	Significant Core Assay Results	9
Table 5	Proposed Exploration Budget	10

List of Figures

Figure 1	Location Map	4
Figure 2	Claim Map.....	5
Figure 3	Regional Geology	7
Figure 4	Property Geology Map.....	in pocket
Figure 5	Au-in-Soils Geochemistry	in pocket
Figure 6	Section GC-04-01	Appendix 3
Figure 7	Section GC-04-02	Appendix 3
Figure 8	Section GC-04-03	Appendix 3
Figure 9	Section GC-04-04	Appendix 3
Figure 10	Section GC-04-05	Appendix 3
Figure 11	Section GC-04-06	Appendix 3

Appendices

Appendix 1	2004/05 Gold Creek Exploration Expenditures
Appendix 2	Statements of Qualifications
Appendix 3	Rock Sample Descriptions
Appendix 4	Drill Sections
Appendix 5	Diamond Drill Logs
Appendix 6	Analytical Procedures/Certificates of Analysis

1.0 Summary

The Gold Creek Property consists of three contiguous claim blocks comprising 58 units covering 1450 hectares within the Kamloops Mining Division, located 90 kilometres north of Kamloops, British Columbia. Navasota Resources Ltd., has a 100% interest in the Gold Creek Property with no royalties payable.

The property is situated immediately south of Birk Creek, a moderately steep, glacially carved, U-shaped valley, extending south along the eastern margin of a subalpine plateau. Access to the property is easily accomplished by a series of all-weather roads from Highway 5 at Barriere, B.C.

Much of the previous mineral exploration activity in the area has centred on the Enargite Showing (MinFile 082M00317). Production from short adits totaled 36 tonnes yielding 3732 grams Ag, 1581kg Cu, 1341kg Pb and 651kg Zn. Navasota conducted a program of soil geochemistry and ground magnetics over the Slate Creek grid at the south end of the property, highlighting a strong gold-in-soil anomaly coincident with linear magnetic trends.

The Slate Creek and Enargite areas were revisited in July 2004. Fifteen rock samples were taken from exposed quartz vein subcrop and outcrop in both areas and 25 soil samples were collected from lines extended to the north from the Slate Creek grid. Results were sufficiently encouraging to recommend the establishment of a grid extending from the Slate Creek grid to the northwest to cover the Enargite Showing area.

A baseline trending 338° was cut and 500 metre winglines were flagged perpendicular to the baseline. The grid was soil sampled and mapped, highlighting several anomalous trends. Six diamond drill holes totaling 883.2 metres were completed in December 2004. Four holes (GC-04-01 to 04) tested a north-northwest trending gold-in-soil geochemical anomaly; one drill hole (GC-04-05) tested a geochemical anomaly 500 metres to the west, and one hole (GC-04-06) tested under the "Enargite Showing" at the north end of the property.

Sampling of drill core from GC-04-01 to 04 showed only weakly anomalous gold values associated with narrow quartz veins hosted in dark phyllite and argillite of the Paleozoic Eagle Bay Group. GC-04-05 intersected weakly altered, fine to medium-grained diorite/gabbro with little veining and very weak gold values. GC-04-06 returned intersections of 645 ppb Au over 0.45 metres and 960 ppb Au over 1.0 metre under the Enargite Showing, between 82.65 and 87.0 metres down hole. Both intervals correspond to quartz veins near an argillite-felsic volcanic contact. Galena and sphalerite are present in minor amounts.

Drilling failed to explain the gold-in-soils anomaly in the south half of the property. At Enargite, GC-04-06 demonstrated that quartz veins near an important regional structure are indeed gold-bearing. Additional geological mapping, rock sampling, ground magnetics and EM survey, and, if warranted, trenching are recommended over the grid. A detailed surface mapping and sampling program is recommended for the Enargite area. Diamond drilling is contingent upon favourable results.

2.0 Introduction

2.1 Terms of Reference

This assessment report details exploration work completed on the Gold Creek Property, located 90 kilometres north of Kamloops, British Columbia. The report is intended to fulfill reporting requirements to apply work credit to the Gold Creek mineral claims. The author supervised the work described herein, and is responsible for all geological interpretations resulting from this fieldwork.

2.2 Property Description, Location, and Access

The Gold Creek Property consists of three contiguous claim blocks comprising 58 units covering 1450 hectares within the Kamloops Mining Division. Navasota Resources Ltd., holds a 100% interest in the property with no royalties payable. The claims have not been legally surveyed.

Table 1
Gold Creek Property Mineral Claims

Claim Name	Tenure No.	Units	Area (ha)	New Expiry Date	NTS
GOLDCREEK	394105	20	500	2011/Aug/16	082M/05W
GOLDCREEK2	395895	18	450	2011/Aug/16	082M/05W
GOLDCREEK3	395896	20	500	2011/Aug/16	082M/05W

The Gold Creek, Gold Creek 2 and 3 mineral claims are located 7 kilometres west of North Barriere Lake in the Adams Plateau area in south-central B.C. The property is found on NTS map 082M/05W overlapping onto 092P/08E to the west. The claims extend 5 kilometres south from Birk Creek, covering the Enargite Showing (MinFile 082M00317) and the headwaters of Slate Creek (Fig 2).

Access to the property is accomplished by a series of all-weather roads. From Barriere, the Barriere Lakes Road extends east from Highway 5. The North Barriere Lake Road branches to the north affording all-weather access to within 10 kilometres of the property. The Birk Creek Forest Access Road branches to the northwest and climbs up to the property, traversing the northern portions of the Gold Creek 2 and 3 claims. The Birk Creek FSR is in good, two wheel drive condition in summer months but is not normally maintained during the winter months. From the Birk Creek FSR, spur roads and skid trails provide excellent access to most areas of the property.

2.3 Climate and Physiography

The Gold Creek Property lies immediately south of Birk Creek, a moderately steep, glacially carved, U-shaped valley, extending south along the eastern margin hummocky plateau. Elevations range from 1400 to 1700 metres falling off sharply to the southeast. The plateau area is gently rolling with 20% marsh area and rounded rock hills covered by sub-alpine forest. Lower elevations have been extensively logged and second growth forests cover much of the area.

Summers in the area are generally warm and dry; winters are moderate with snow on the ground between October and May. At Blue River, annual precipitation averages 959 millimetres, including 426 centimetres of snow. Temperatures range from -13°C in January to 24°C in July.

2.4 Property History

Between 1936 and 1952, the Enargite Showing, in the north part of the Gold Creek 2 claim, saw hand mining in a short adit shipping 36 tonnes yielding 3732 grams Ag, 1581kg Cu, 1341kg Pb and 651kg Zn. Little other work was recorded until 1979. Limited trenching on deformed quartz veins found spotty high-grade lead-zinc-silver mineralization.

In 1984, a horizontal loop EM survey covered the Northstar area, 1.5km southeast of Enargite, outlining several linear anomalies. Five diamond drill holes were completed with mixed results. Hole 84-1 intersected 7.65 g/t Au, 14.06 g/t Ag over 0.94 metres at 72 metres depth in pyritic siltstone hosting moderate quartz veining. Hole 84-3 intersected graphitic argillities with one pyritic section returning 1.99 g/t Au over 0.9 metres.

In 1985, Noranda Exploration conducted an airborne magnetics and EM survey north of the Gold Creek property. Two NW trending conductors and a near coincident magnetic anomaly were defined in rocks of the Eagle Bay Assemblage (EBA), while a very strong north trending conductor roughly coincides with the EBA/Fennell Formation thrust contact.

In 1986, the Joe claims were located in the area of the current Gold Creek 1 claim. Samples of quartz vein hosting galena and sphalerite with significant gold values were noted.

The Gold Creek claim was staked in June 2002, followed by Gold Creek 2 and 3 later in August 2002. A compass and chain grid was established over Slate Creek with a 1-kilometre east-west baseline and north-south winglines extending 300 metres north and south of the baseline. Soil samples were taken at 25 metre intervals along the winglines and analyzed for gold (fire assay) and 20 other elements (ICP). Samples were taken from the base of pits dug into B horizon strata typically 30 – 50cm deep. Gold-in-soil results were plotted and contoured, outlining a north-south and east-southeast trending anomaly. Two deeper (~1m) test pits were dug at the upslope end of the highest (up to 430 ppb Au) soil anomaly and sampled down profile. These pits show Au values increasing with depth (Warner and Kay, 2003).

Later in the fall of 2002, a ground magnetometer survey was conducted over the area highlighted by soil geochemistry. A Scintrex MP-2 magnetometer measured total field intensity readings of the Earth's magnetic field at 12.5m stations along 100m spaced lines across the grid. Duplicate readings of control points along the baseline were compared and used to correct for diurnal variation. Profiles of magnetic intensity show a series of linear trends approximately parallel to high gold-in-soil soil anomalies and interpreted regional scale structures.

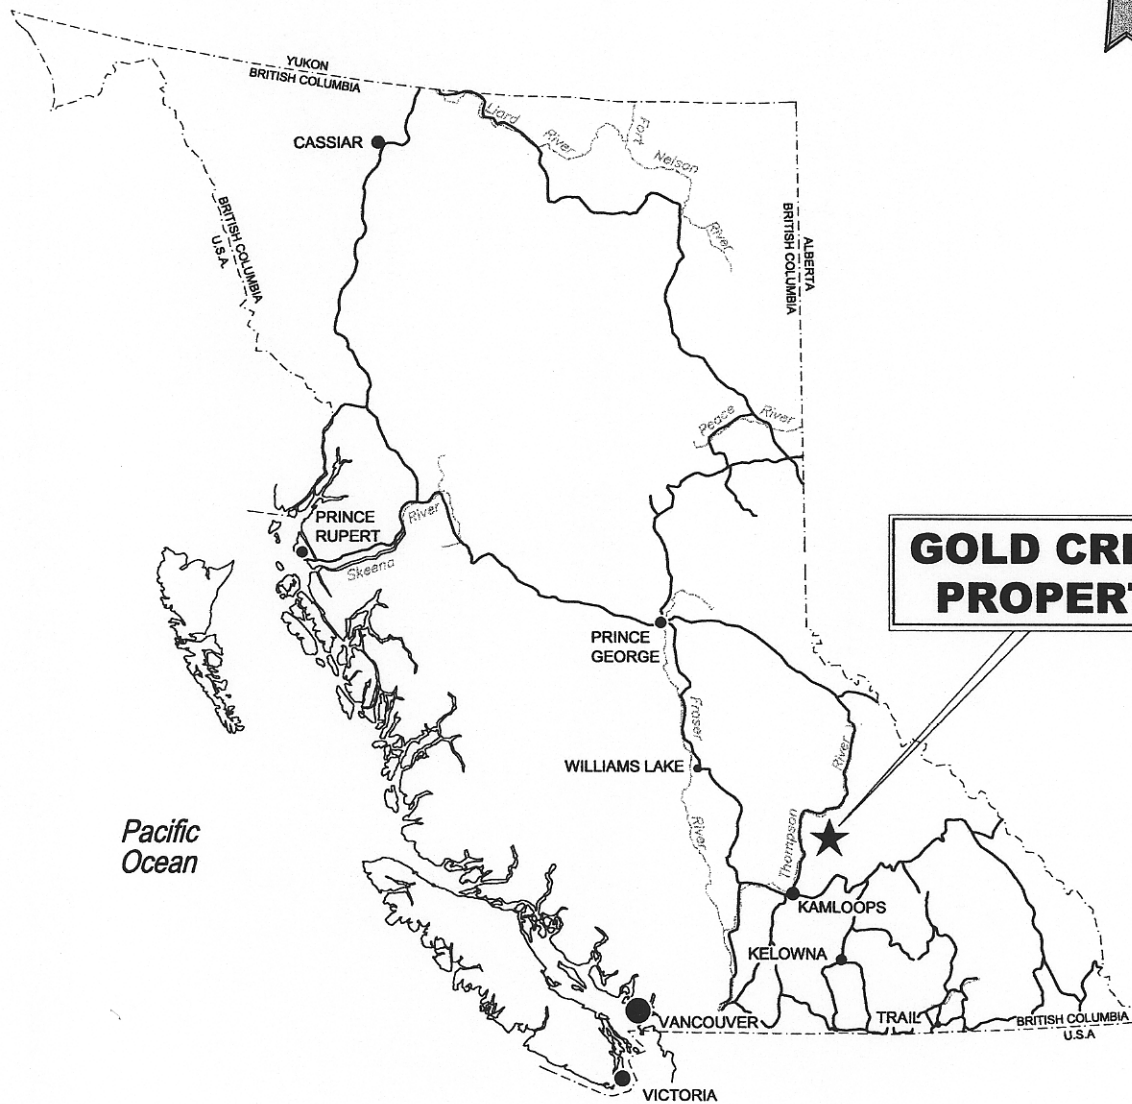
2.5 2004-05 Program

The Slate Creek and Enargite areas were revisited in July 2004. Fifteen rock samples were taken from exposed quartz vein subcrop and outcrop in both areas and 25 soil samples were collected from lines extended to the north from the Slate Creek grid. Results were sufficiently encouraging to recommend the establishment of a grid extending from the Slate Creek grid to the northwest to cover the Enargite Showing area.

A baseline trending 338° was cut and 500 metre winglines were flagged at 100 or 200-metre intervals perpendicular to the baseline. The grid was soil sampled and mapped, highlighting several anomalous trends. A program of 6 diamond drill holes totaling 883.2 metres commenced in December 2004. Four holes (GC-04-01 to 04) tested a north-northwest trending gold-in-soil geochemical anomaly; one drill hole (GC-04-05) tested a geochemical anomaly 500 metres to the west, and one hole (GC-04-06) tested under the Enargite Showing at the north end of the property.

Sampling of drill core from GC-04-01 to 04 showed only weakly anomalous gold values associated with narrow quartz veins hosted in dark phyllite and argillite of the Paleozoic Eagle Bay Group. GC-04-05 intersected weakly altered, fine to medium-grained diorite with little veining and very weak gold values. GC-04-06, under the Enargite Showing, returned intersections of 645 ppb Au over 0.45 metres and 960 ppb Au over 1.0 metre between 82.65 and 87.0 metres down hole. Both intervals correspond to quartz veins near an argillite - felsic volcanic contact. Galena and sphalerite are present in minor amounts.

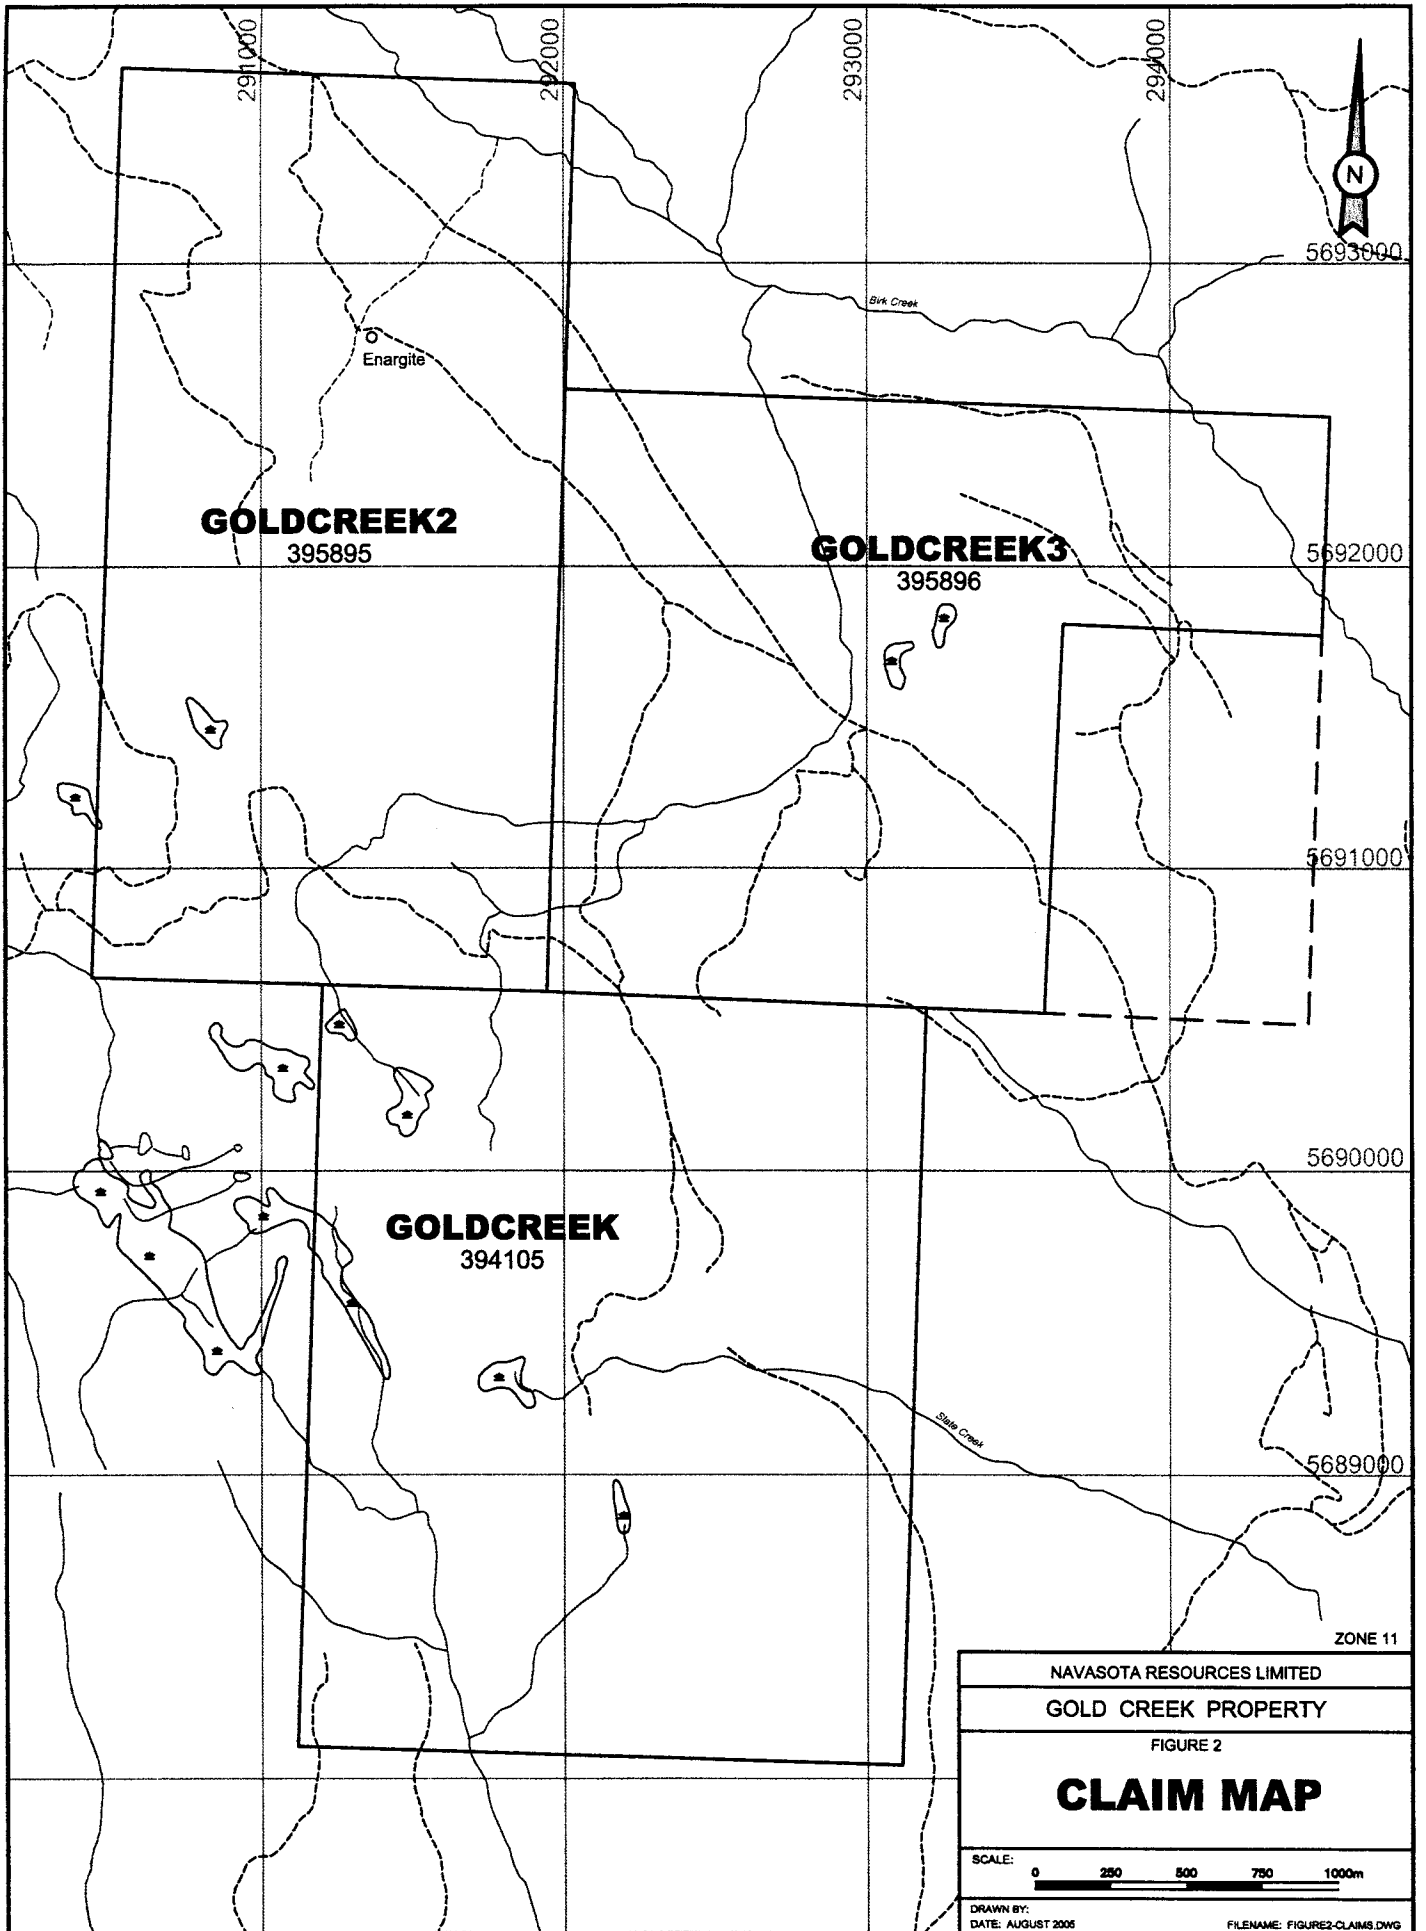
Drilling failed to explain the gold-in-soils anomaly in the south half of the property. At Enargite, GC-04-06 demonstrated that quartz veins near an important regional structure are indeed gold-bearing. A detailed surface mapping and sampling program is recommended for the Enargite area.



**GOLD CREEK
PROPERTY**

*Pacific
Ocean*

NAVASOTA RESOURCES LIMITED
GOLD CREEK PROPERTY
FIGURE 1
LOCATION MAP
SCALE: 0 100 200 300 400 500km
DRAWN BY: WILDRICK RESOURCES DATE: AUGUST 2005
FILENAME: FIGURE1-LOCATION.DWG



3.0 Geological Setting

3.1 Regional Geology

The Birk Creek area is underlain by Paleozoic rocks of the Eagle Bay Assemblage and Fennell Formation. The Eagle Bay Assemblage consists of Early Cambrian to Mississippian metasedimentary and metavolcanic rocks that are locally intruded by Devonian orthogneiss (Schiarizza and Preto, 1987). Eagle Bay rocks are part of the pericratonic Kootenay terrane. The Fennell Formation comprises Devonian to Permian oceanic rocks of Slide Mountain terrane, which were thrust over Eagle Bay rocks in early Mesozoic times. Fennell and Eagle Bay rocks were deformed and metamorphosed together; the metamorphic grade is lower greenschist through most of the area. Both Fennell and Eagle Bay rocks are cut by mid-Cretaceous granitic rocks of the Raft and Baldy batholiths, and by Early Tertiary quartz feldspar porphyry, basalt and lamprophyre dikes. They are locally overlain by Eocene sedimentary and volcanic rocks of the Kamloops Group and by Miocene plateau lavas.

3.2 Property Geology

3.2.1 Lithology

The Gold Creek Property straddles the thrust contact of the Fennell Formation over the Eagle Bay Assemblage to the east (Figure 3). Although outcrop exposure is only 2%, bedrock and regolith mapping on the property confirms that the west side of the property is underlain by bedded chert, chert breccia, rhyolite, gabbro/diorite and mafic volcanics of the Fennell (Figure 4). Mapping west of the grid highlighted the lower Fennell sequence of chert breccia, mafic flows, and diorite. Diorite dominates a ridge running down the southern half of the west side of the grid. Diorite and mafic flows lie southwest of Enargite. Several knobs of rhyolite lie west of the diorite unit, southwest of the grid.

Dark, locally recessive argillite and siltstone (grey phyllite) and minor limestone of the Eagle Bay underlie the eastern half of the property. The thrust contact is interpreted to run through the Enargite Showing, south-southeast along the base of the diorite ridge, through the centre of the Slate Creek grid. The contact appears to dip steeply to the west.

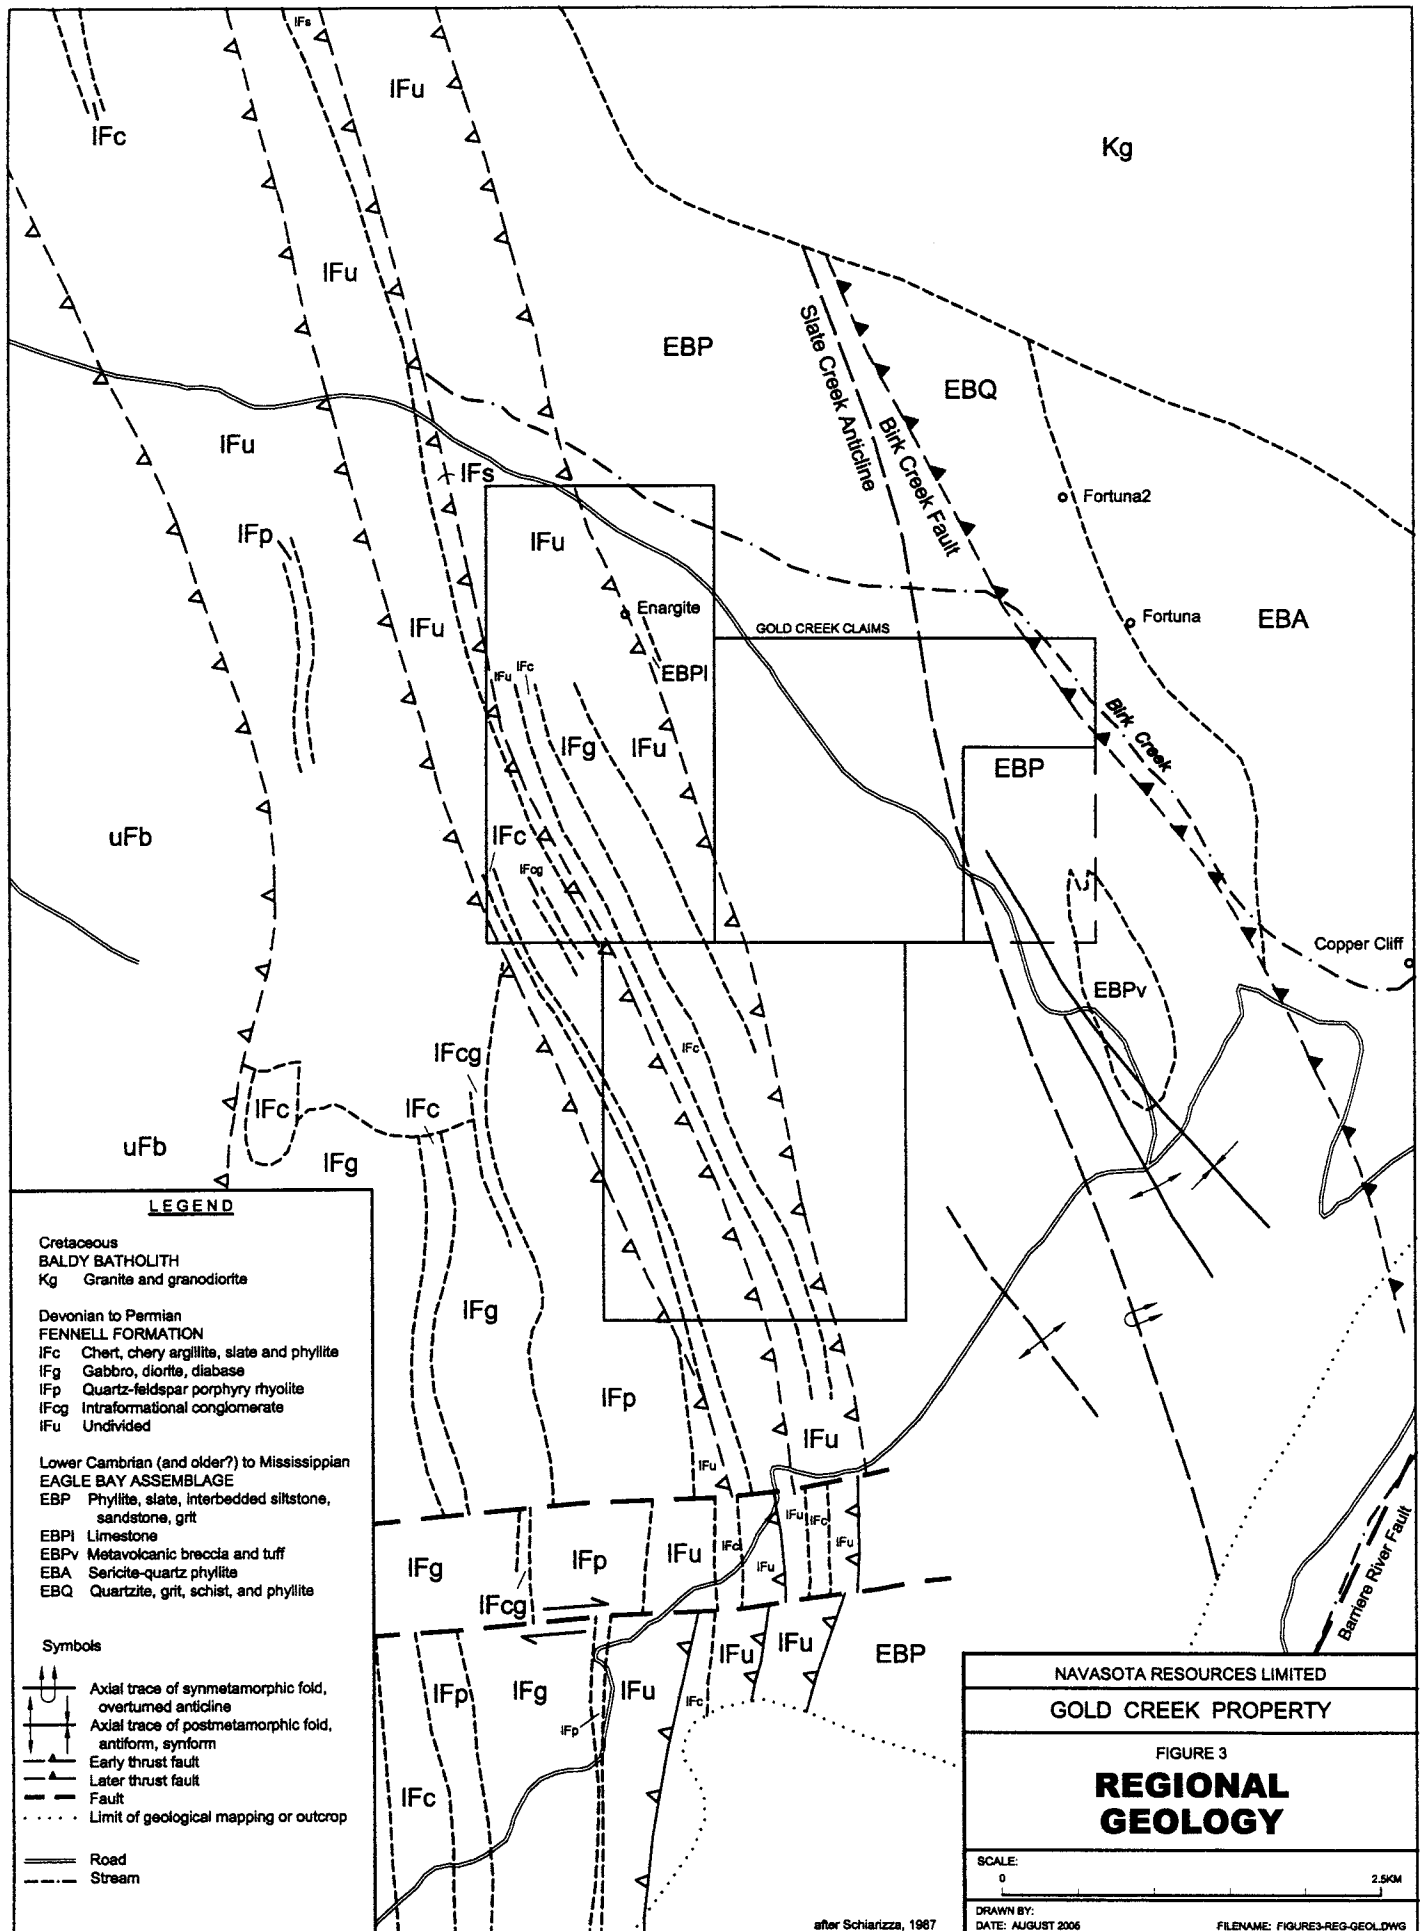
3.2.2 Structure and Mineralization

At Enargite, mineralized quartz veins and shears are confined to the contact zone between gabbro/diorite to the west and dark phyllites to the east. Mineralization consisting of galena, pyrite and lesser sphalerite and chalcopyrite, is hosted in quartz veins within a zone some 200 metres north-south by 120 metres east-west. Individual veins and lenses vary from a few centimetres to several metres wide and vary in orientation, although northerly strikes and moderate (40° to 50°) easterly dips predominate.

Immediately north of Slate Creek, mineralization appears to be just east of the inferred contact. A number of white quartz veins, 30-150 centimetres in thickness were uncovered in subcrop and outcrop. Chip sampling returned several moderately anomalous results. In the area, Warner and Kay (2003) interpreted a previously unmapped, northwest-trending linear structure cutting the inferred thrust contact.

Table 2
Significant Rock Sample Results

Sample	Area	Description	Au ppb	Au g/t	Ag g/t	Pb %	Zn %
QV-04-005	Slate Cr	White quartz vein	665				
GK-04-009	Enargite	Quartz vein, gal, sph	>1000	6.14	640	29.0	12.1
GK-04-010	Enargite	White quartz vein	75				
GK-04-022	Slate Cr	Quartz vein	425				
GK-04-042	Central	Rusty argillite (sericite).	135				
GK-04-044	Enargite	Green unit (sil seds?)	670				
GK-04-051	Enargite	Quartz vein	90				



4.0 Soil and Rock Geochemistry

In July 2004, 25 soil samples were collected from lines extending from the north ends of lines 102E and 103E on the previously established Slate Creek Grid (Figure 5). Six of the samples returned values in excess of 100 ppb with a high value of 305 ppb and 5 more in excess of 50 ppb. These anomalous values line up well with a northwest-trending anomalous zone described by Warner and Kay (2003).

These initial results provided the impetus to establish a grid running from the Slate Creek grid, north-northwest to the Enargite Showing. Baseline 5000E was cut from 20000N, at the north end of the Slate Creek grid, to 23800N, approximately 300 metres northwest of the Enargite Showing, a total distance of 3.8 kilometres. Winglines were flagged 500 metres east and west of the baseline at a 100-metre spacing from 20000N – 21600N and 23000 – 23800N, and at 200-metre spacing between 21600N – 23000N (Figure 5). Soil samples were collected at 25-metre intervals along the winglines and the baseline.

Soil development at Gold Creek is poor. In most places, the soil profile consists of 2-5 centimetres of black humus (A-horizon) over a weakly developed to absent brown to orange B-horizon. A thin, grey leached horizon is sometimes present. Most samples were collected in brown rocky soil (C-horizon), less than 30 centimetres deep, often less than 15 centimetres. Grey phyllite and black argillite were the most common rock type found in soil samples. In places, organic soil extended to depths greater than 50 centimetres, and was collected in those locales. A total of 1393 soil samples were collected and analyzed.

Soil samples were delivered to Eco Tech Laboratory Ltd.'s Kamloops facilities for analysis. Samples were dried, sieved to -80 mesh, and analyzed for gold by geochemical gold analysis and for 28 elements by ICP (see complete description of methodology in Appendix 4).

Over most of the grid, gold values are typically 10 ppb or less. In the Slate Creek area, gold-in-soils range up to 985 ppb, with 12 samples returning values over 100 ppb, most of those within 100 metres of the baseline. These data support previous data from the Slate Creek grid. Along the west side of new grid, 6 samples analyzed over 100 ppb. Four soil samples from the Enargite area returned values over 100 ppb, including 2 over 1000 ppb. Interestingly, surrounding soils are at background values.

Over the south half of the grid, anomalous gold is coincident with slightly elevated Ag, As, Pb and Zn. Base metal values are also weakly anomalous along the east side of the grid. High gold values in soil at Enargite are coincident with very high Ag (>30 ppm), Pb (up to 9570 ppm), and moderate As, Cu, Fe and Zn. Weak Pb-Zn (+/-Ag) anomalies are coincident with the projected trend of gold mineralization.

A total of 47 rock grab and chip samples were collected from subcrop and outcrop around the grid (Figure 4). Table 2 highlights the significant results. A sample of galena and sphalerite-rich quartz vein assayed 6.14 g/t Au in addition to 640 g/t Ag, 29.0% Pb, and 12.1% Zn. Two samples of white quartz veins north of Slate Creek assayed 665 ppb and 425 ppb Au, but several others returned only background values of gold, silver and base metals. Rock samples were also analyzed for Au by geochemical analysis and for 28-elements by ICP.

5.0 Diamond Drilling

A program of six diamond drill holes totaling 883.6 metres was completed at Gold Creek in December 2004 (Table 3). The drilling contractor was Frontier Drilling Corp., of Kamloops, B.C. Four drill holes targeted a zone of mapped quartz veining, coincident with gold-in-soil anomalies, over the southern half of the grid. One hole tested an isolated gold-in-soil anomaly along the west side of the grid. The final hole tested the Enargite Showing, extending under the upper adit.

Table 3
Summary of Diamond Drill Holes

DDH	Northing	Easting	Azimuth	Dip	Depth-m
GC-04-01	5689963	262416	068	-45	148.5
GC-04-02	5689687	292494	068	-45	151.7
GC-04-03	5690152	292355	248	-45	148.5
GC-04-04	5690533	292214	248	-45	151.5
GC-04-05	5690711	291706	248	-45	148.4
GC-04-06	5692755	291435	260	-45	135.0
					883.6

5.1 Slate Creek Area

Four diamond drill holes (GC-04-01 to 04) were completed north of Slate Creek. All four intersected a monotonous sequence of dark grey to black phyllitic argillite, punctuated by white quartz veining up to 0.5 metres thick (Figures 6 – 9). Graphitic slip planes and 5-25 centimetres thick fault breccia zones are common. Coarse cubic diagenetic pyrite is ubiquitous. Two veins in GC-04-04 returned significant assays (see Table 4).

Table 4
Significant Core Assay Results

DDH	From	To	Interval	Au- g/t
GC-04-02	33.40	34.90	1.50	0.13
	87.90	88.90	1.00	0.12
GC-04-04	34.20	35.20	1.00	0.39
	141.00	142.00	1.00	0.35
GC-04-06	82.65	83.10	0.45	0.65
	86.00	87.00	1.00	0.96

5.2 Central Area

One diamond drill hole (GC-04-05) was completed at the west end of L21400N in the central part of the grid. The entire hole consists of fine to coarse grained diorite and/or gabbro (Figure 10). Alteration consists of pervasive chlorite, minor epidote, quartz and carbonate with sections of coarse cubic pyrite. None of the 6 samples split assayed greater than 0.02 g/t Au.

5.3 Enargite Showing

One diamond drill hole (GC-04-06) tested under the upper adit of the Enargite Showing area. The hole was collared in argillite east of the showing, passing through a series of narrow unmineralized white quartz veins. The thrust fault zone was marked by a coarse, polymictic, moderately silicified fault breccia, passing into altered diorite (quartz-feldspar porphyry) and back into mineralized argillite (Figure 11). The hole terminated in strongly altered (silica-sericite) felsic breccia and tuff breccia. Two samples returned significant gold values (see Table 4), both in altered argillite between the diorite and felsic units. The tectonic setting and widespread alteration make the Enargite zone a significant target for gold, silver and base metal mineralization.

6.0 Conclusions and Recommendations

A program of line cutting, soil and rock geochemistry, geological mapping, and diamond drilling was completed on the Gold Creek Property in the second half of 2004. Follow-up soil geochemistry demonstrated that gold-in-soil anomalies discovered in the Slate Creek area are coincident with mapped quartz vein subcrop and outcrop. Expanded soil geochemistry coverage outlined the Slate Creek and Enargite targets.

Diamond drilling late in the season tested both areas. In the Slate Creek area, minor white quartz veining hosted in dark grey to black argillite returned weakly anomalous gold values. At Enargite, a hole drilled under the upper adit returned results of 0.65 g/t Au over 0.45 metre and 0.96 g/t Au over 1.0 metre from mineralized argillite in fault contact with felsic volcanics and altered dioritic rock.

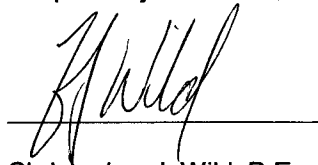
These results demonstrate that gold mineralization is found along the regionally significant thrust contact between Eagle Bay sedimentary rocks and mafic to felsic rocks of the Fennell Formation. Drill holes targeting the southern half of the grid (GC-04-01 to 04) encountered only Eagle Bay argillites, suggesting that they were collared east of the "Contact Zone".

In view of these conclusions, a follow-up program of detailed mapping and sampling, trenching and diamond drilling is proposed for both the Slate Creek and Enargite targets. Detailed mapping and sampling of the Enargite area will allow correlation with GC-04-06, generating additional drill targets. In the Slate Creek area, further mapping to identify the precise location of the thrust contact is required. Identified quartz veins will be located more precisely, trenched, mapped and sampled. A ground-based magnetometer and VLF-EM survey is also recommended. Should results warrant, diamond drilling would follow. Table 5 provides an outline budget of the suggested program.


Table 5
Proposed Exploration Program Budget

Geological Mapping					
	20	days	\$ 500.00	per day	\$ 10,000.00
	20	days	\$ 200.00	per day	\$ 4,000.00
Grab and Chip Sampling					
	60	samples	\$ 25.00	per sample	\$ 1,500.00
Geophysics					
	35	line km	\$ 200.00	per km	\$ 7,000.00
Trenching					
	50	hours	\$ 150.00	per hour	\$ 7,500.00
Diamond Drilling					
	1000	metres	\$ 85.00	per metre	\$ 85,000.00
Total					\$ 115,000.00

Respectfully submitted,



Christopher J. Wild, P.Eng.
Consulting Geological Engineer
September 12, 2005



7.0 References

Schiarizza, P. and Preto, V.A. (1987): Geology of the Adams Plateau – Clearwater – Vavenby Area. B.C. Ministry of Energy, Mines, and Petroleum Resources, Mineral Resources Division, Geological Survey Branch; Paper 1987-2.

Schiarizza, P. and Preto, V. (1983): Geology of the Barriere River – Clearwater Area, NTS 82M/4, 5, 12; 92P/1, 8, 9. B.C. Ministry of Energy, Mines, and Petroleum Resources Preliminary Map #53.

Warner, L.M. and Kay, B.G. (2003): Assessment Report on the Gold Creek Property, Kamloops Mining Division. B.C. Ministry of Energy and Mines Assessment Report, 11 pages.

Appendix 1

2004/05 Gold Creek Exploration Expenditures


Diamond Drilling					
Drill	2878	feet	\$ 22.60	\$ 65,032.00	
Cat	97	hours	\$ 90.00	\$ 8,730.00	
Grader				\$ 900.00	
Skidoo	3	weeks	\$ 500.00	\$ 1,500.00	
Room & Board	83	mandays	\$ 70.00	\$ 5,810.00	
					\$ 81,972.00
Laboratory Analyses					
Rocks	47	samples	\$ 20.07	\$ 943.42	
Soils	1418	samples	\$ 16.45	\$ 23,322.56	
Core	64	samples	\$ 19.16	\$ 1,226.21	
					\$ 25,492.18
Line cutting & Soil Sampling					
Durfeld Geological				\$ 21,251.33	
					\$ 21,251.33
Personnel					
Robin Whiteaker	14	days	\$ 400.00	\$ 5,600.00	
Christopher J. Wild, P.Eng.	37.50	days	\$ 400.00	\$ 15,000.00	
Royanna Wild	19.75	days	\$ 200.00	\$ 3,950.00	
Roy Holder	14	days	\$ 140.00	\$ 1,960.00	
Andy Silver	1	days	\$ 300.00	\$ 300.00	
Larry Durant	1	days	\$ 350.00	\$ 350.00	
					\$ 27,160.00
Vehicle					
Wildrock Resources	4861	km	\$ 0.50	\$ 2,430.50	
Whiteaker	840	km	\$ 0.40	\$ 336.00	
Pick-up (Whiteaker)				\$ 1,417.83	
Gas for Pick-up				\$ 252.44	
					\$ 4,436.77
Drafting & Report					
Royanna Wild	33	hours	\$ 25.00	\$ 825.00	
Drafting	28.75	hours	\$ 40.00	\$ 1,150.00	
Data Entry	14	hours	\$ 16.00	\$ 224.00	
Misc				\$ 18.77	
					\$ 2,217.77
Miscellaneous					
Office	4	months	\$ 425.00	\$ 1,700.00	
Trapline				\$ 750.00	
Supplies & Expenses	Wildrock			\$ 351.44	
	Whiteaker			\$ 136.52	
					\$ 2,937.96
					Total \$ 165,468.01

Appendix 2


Statements of Qualifications

I, Christopher J. Wild, do hereby certify that:

- 1 I am a consulting geological engineer currently residing at 2416 Abbeyglen Way, Kamloops, British Columbia.
- 2 I am a graduate of the University of British Columbia, Geological Engineering, Mineral Exploration Option (1984).
- 3 I have worked in mineral exploration and mine geology in Canada, West Africa, and Argentina on a full-time basis since 1985.
- 4 I am Registered Member of the Association of Professional Engineers and Geoscientists of the Province of British Columbia (1994), and am a member of the Canadian Institute of Mining and Metallurgy (CIM).
- 5 I supervised all exploration activity documented in this report.
- 6 I am currently President and CEO of Navasota Resources Ltd.



Christopher J. Wild, P.Eng.
Consulting Geological Engineer



September 12, 2005

Appendix 3

Rock Sample Descriptions

Sample Number	Rock	Grid x	Grid y	Utm x	Utm y	GPS Waypoint #
QV-04-001	Quartz vein in diorite o/c					
QV-04-002	Weakly limonitic quartz vein subcrop					
QV-04-003	White quartz veining in dark phyllite					
QV-04-004	50cm white quartz vein					
QV-04-005	White quartz vein float in tree roots					
GK-04-006	Cherty tectonic breccia					
GK-04-007	Dark green, f-gr ultramafic dyke					
QV-04-008	White quartz vnlt in ultramafic host					
GK-04-009	Quartz vein; galena + sphalerite					
GK-04-010	Quartz vein in smaller adit					
GK-04-011	Quartz vein in wall of adit					
GK-04-012	Quartz vnlt in argillite					
GK-04-013	Quartz vnlt in argillite					
GK-04-014	Quartz vnlt in argillite					
GK-04-015						
GK-04-020	buff/beige weath, rhy?	4650	20100			70
GK-04-021	qv float					85
GK-04-022	qv					97
GK-04-023	Fe carb dior?					97
GK-04-024	Arg with qv stckwrk			292250	5690046	3
GK-04-025	qv float (30cm)	4880	20535			
GK-04-026	arg, sil, wk carb	4875	20490			
GK-04-027	arg, str alt (carb), float	4910	20600			
GK-04-028	qv, subcrop, may be outcrop	4832	20600	292224	5690097	7
GK-04-029	alt arg; qtz ser alt	4800	20642			
GK-04-030	qv outcrop or subcrop	4823	20600			
GK-04-031	qv and fe carb alt dior, qvs to 2cm	4680	20807	292048	5690150	26
GK-04-032	qv in outcrop (70cm chip)			292226	5690203	43

Sample Number	Rock	Grid x	Grid y	Utm x	Utm y	GPS Waypoint #
GK-04-033	very silic. Altered rock			292226	5690203	43
GK-04-034	host rock (sil arg) to sample 032			292226	5690203	43
GK-04-035	Fe carb dior					5
GK-04-036	ser-qtz alt rx, pale grey/green	4755	20905			
GK-04-037	same as 036, v. hard, qtz-ser (fe-carb wk?)					8
GK-04-038	interbedded seds (chert/arg?)			292098	5690277	21
GK-04-039	qv, appears in place but may be subcrop. Abundant quartz float around. Arg host??	4824	21200	291966	5690650	33
GK-04-040	Strong Fe-Carb/Limonite Altered Rock (Dior)			291955	5690767	203
GK-04-041	QV	4700	20995			
GK-04-042	Argillite - "Chewed Up", Rusty, possible Sericite alteration	4835	20985			
GK-04-043	buff/beige weath, massive			291305	5692600	225
GK-04-044	Green unit (sil seds?)			291361	5692735	229
GK-04-045	Quartz in outcrop (rusty surfaces, otherwise bull qtz)	5040	23080			(same location as GK-04-012)
GK-04-046	Fresh Diorite			292123	5689176	320
GK-04-047	Diorite			291766	5690789	321
GK-04-048	qtz			291334	5692741	336
GK-04-049	Fe carb Diorite			291334	5692741	336
GK-04-050	Grit?, Near adit			291376	5692785	341
GK-04-051	QV			291340	5692840	342

Appendix 4
Drill Sections

GC-04-01
 Az: 068°
 Dip: -45°

Casing

22588

22589

22590

Argillite

22591

22592

22593

22594

22595

22596


DDH	Sample No	From	To	Interval	Au g/t
GC04-01	22588	23.50	25.00	1.50	<0.03
GC04-01	22589	48.60	50.10	1.50	<0.03
GC04-01	22590	58.70	58.70	2.00	0.06
GC04-01	22591	78.70	80.70	2.00	0.03
GC04-01	22592	85.50	86.50	1.00	<0.03
GC04-01	22593	93.80	94.80	1.00	<0.03
GC04-01	22594	105.60	108.60	3.00	0.04
GC04-01	22595	136.90	138.90	2.00	0.04
GC04-01	22596	148.90	147.90	1.00	<0.03

EOH = 148.5m

NAVASOTA RESOURCES LTD.

GOLD CREEK PROPERTY

SECTION GC-04-01



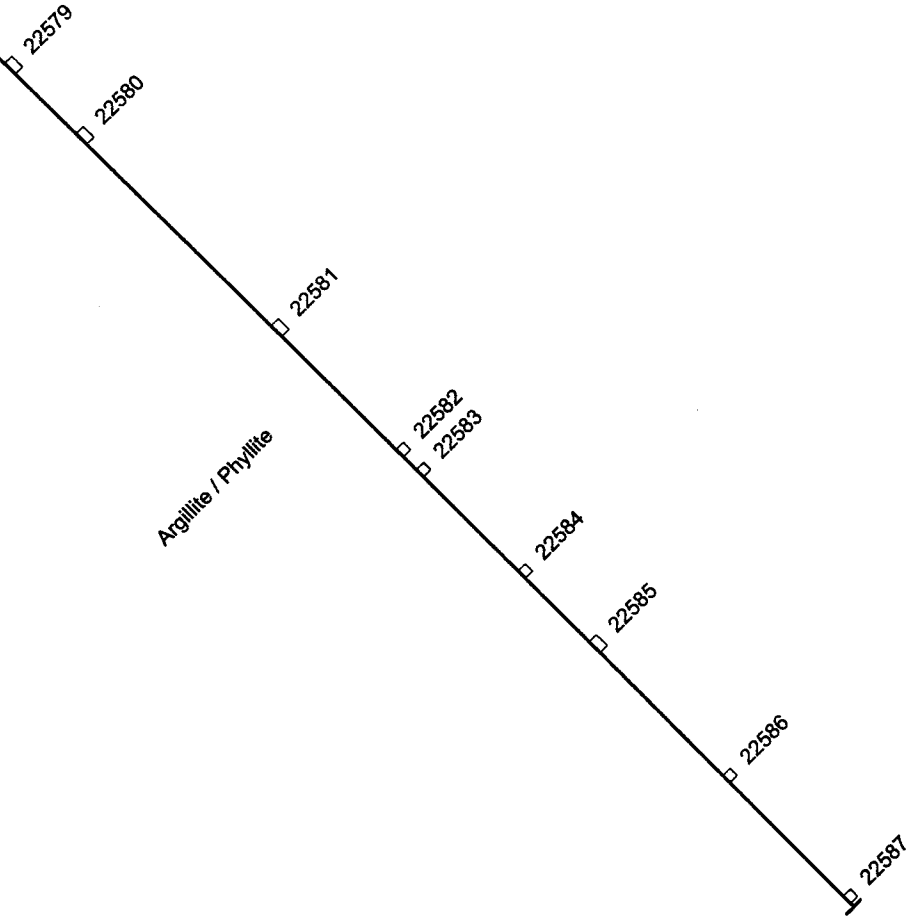
DRAWN BY: rlv
 DATE: August 2005
 FILENAME: FIGURE8-SECTION-GC04-01.dwg

FIGURE
 6

GC-04-02
 Az: 068°
 Dip: -45°

Casing

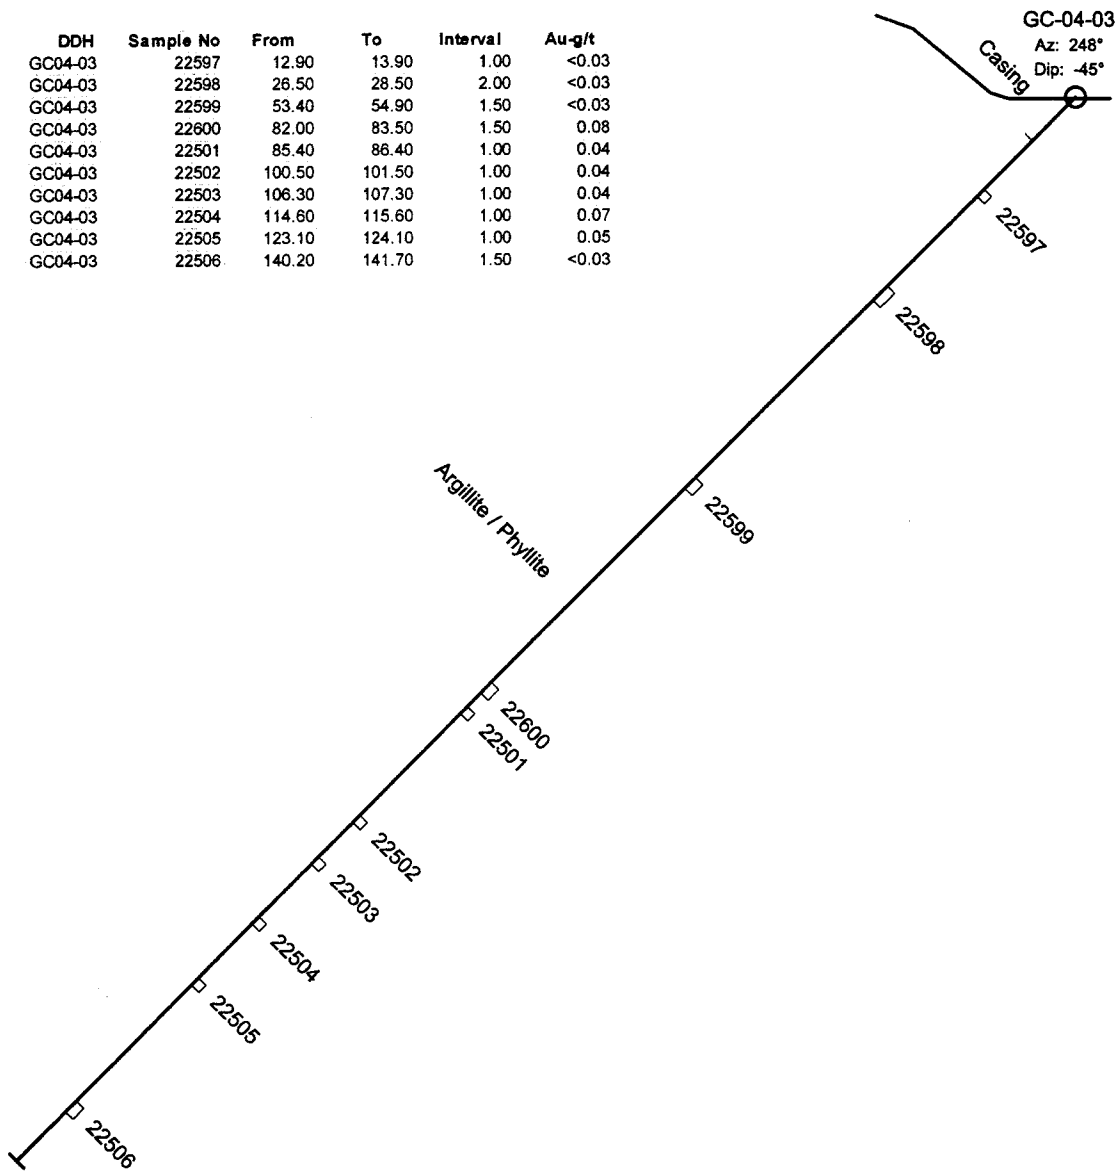
DDH	Sample No	From	To	Interval	Au g/t
GC04-02	22579	33.40	34.90	1.50	0.13
GC04-02	22580	43.30	44.80	1.50	<0.03
GC04-02	22581	70.50	72.00	1.50	0.03
GC04-02	22582	87.90	88.90	1.00	0.12
GC04-02	22583	90.70	91.70	1.00	0.05
GC04-02	22584	104.90	105.90	1.00	<0.03
GC04-02	22585	114.80	116.30	1.50	0.05
GC04-02	22586	133.40	134.40	1.00	0.04
GC04-02	22587	150.20	151.20	1.00	0.03



EOH = 151.7m

NAVASOTA RESOURCES LTD.	
GOLD CREEK PROPERTY	
SECTION GC-04-02	
SCALE: 0 10 20 30 40m	
DRAWN BY: djw DATE: August 2006 FILENAME: FIGURE7-SECTION-GC04-02.dwg	FIGURE 7

DDH	Sample No	From	To	Interval	Au-g/t
GC04-03	22597	12.90	13.90	1.00	<0.03
GC04-03	22598	26.50	28.50	2.00	<0.03
GC04-03	22599	53.40	54.90	1.50	<0.03
GC04-03	22600	82.00	83.50	1.50	0.08
GC04-03	22501	85.40	86.40	1.00	0.04
GC04-03	22502	100.50	101.50	1.00	0.04
GC04-03	22503	106.30	107.30	1.00	0.04
GC04-03	22504	114.60	115.60	1.00	0.07
GC04-03	22505	123.10	124.10	1.00	0.05
GC04-03	22506	140.20	141.70	1.50	<0.03



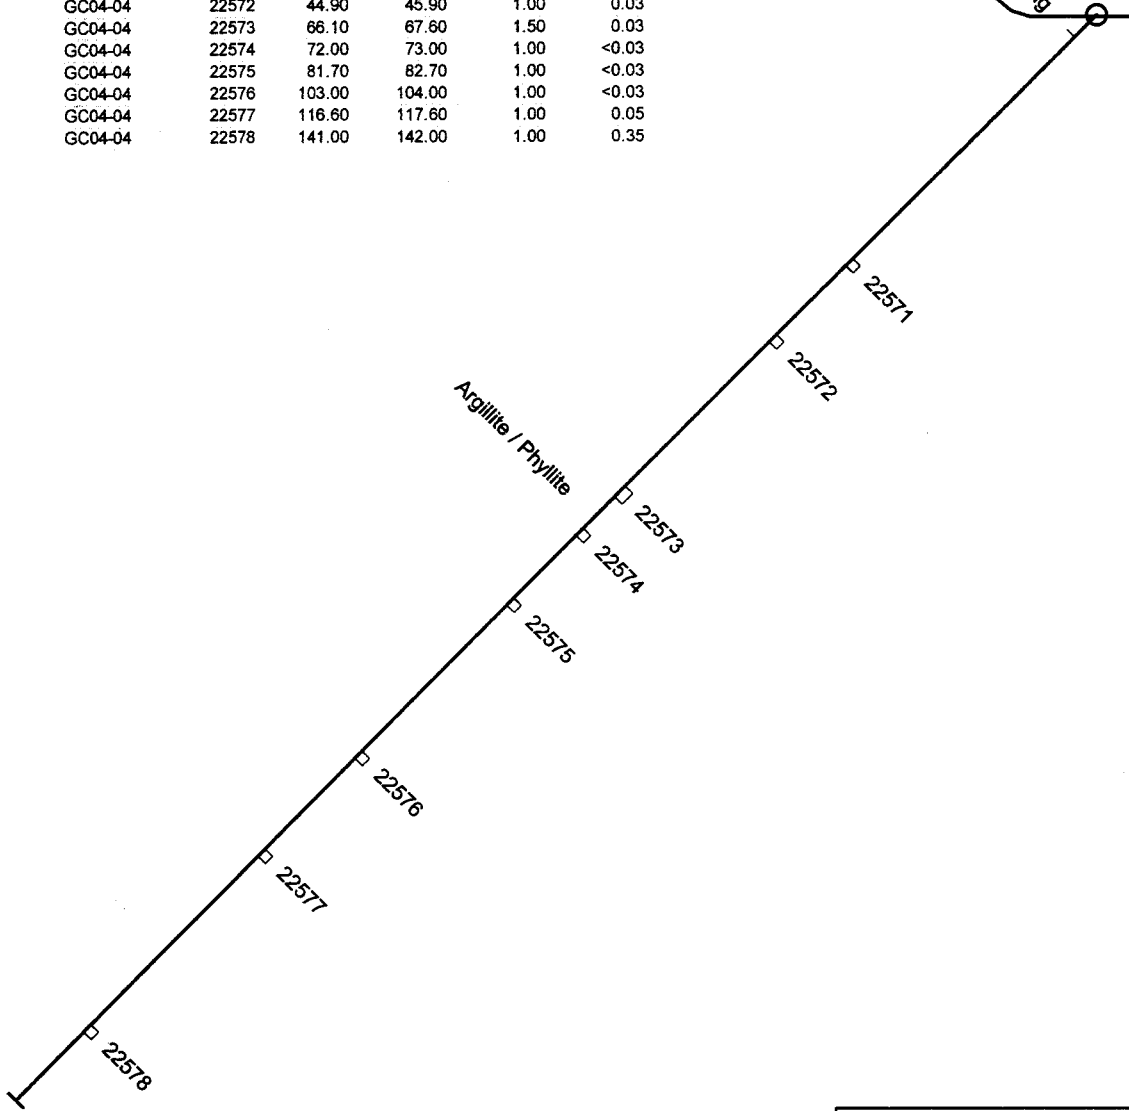
EOH = 148.5m

NAVASOTA RESOURCES LTD.	
GOLD CREEK PROPERTY	
SECTION GC-04-03	
SCALE: 0 10 20 30 40m	
DRAWN BY: rjr DATE: August 2005 FILENAME: FIGURE8-SECTION-GC04-03.dwg	FIGURE 8

DDH	Sample No	From	To	Interval	Au g/t
GC04-04	22571	34.20	35.20	1.00	0.39
GC04-04	22572	44.90	45.90	1.00	0.03
GC04-04	22573	66.10	67.60	1.50	0.03
GC04-04	22574	72.00	73.00	1.00	<0.03
GC04-04	22575	81.70	82.70	1.00	<0.03
GC04-04	22576	103.00	104.00	1.00	<0.03
GC04-04	22577	116.60	117.60	1.00	0.05
GC04-04	22578	141.00	142.00	1.00	0.35

GC-04-04
Az: 248°
Dip: -45°

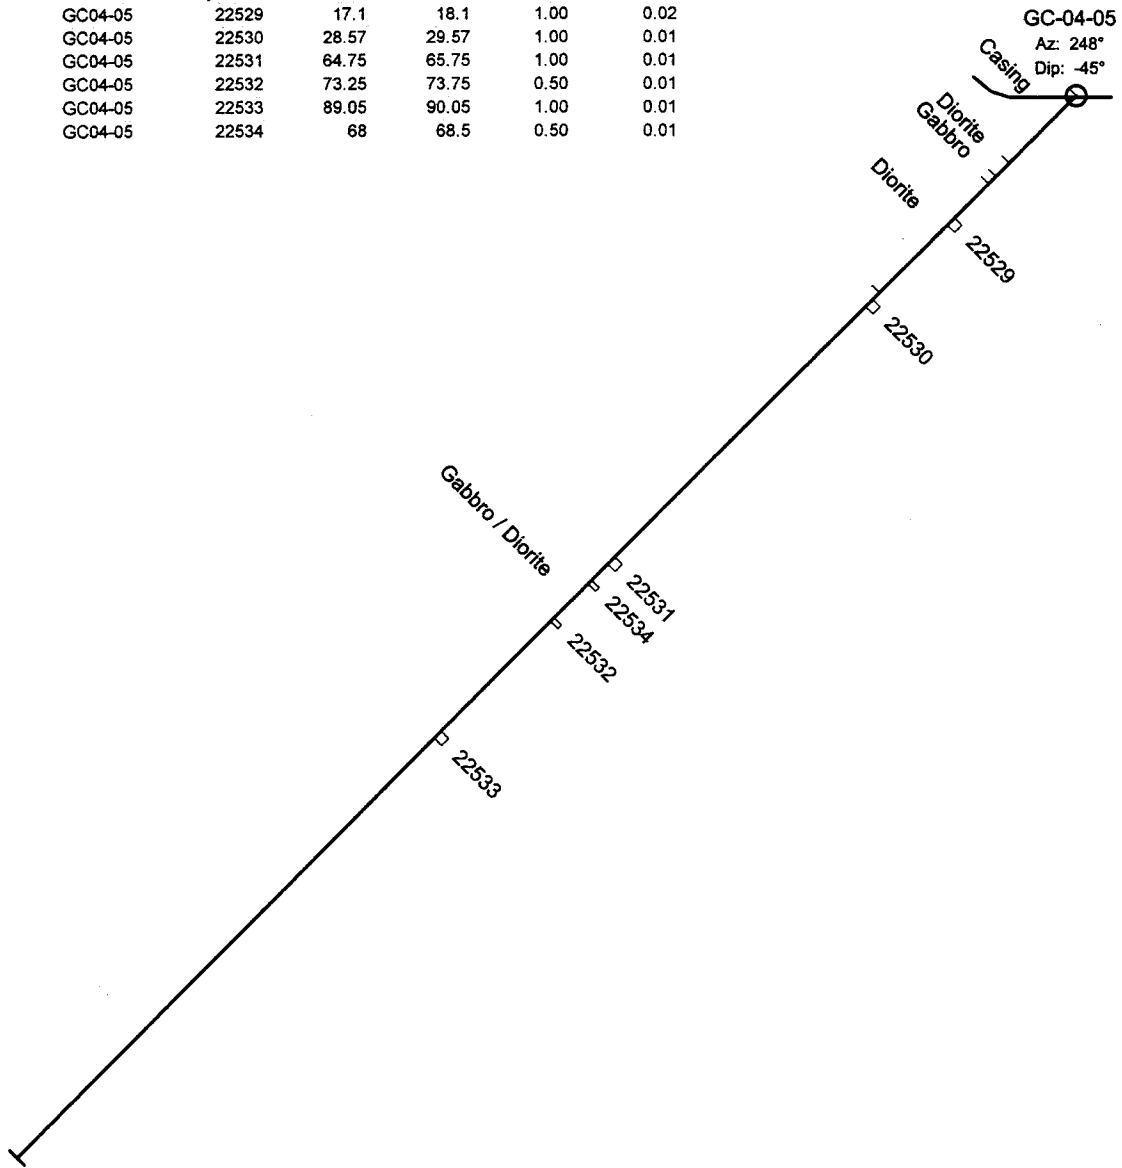
Casing



EOH = 151.5m

NAVASOTA RESOURCES LTD.	
GOLD CREEK PROPERTY	
SECTION GC-04-04	
SCALE: 0 10 20 30 40m	
DRAWN BY: fhw DATE: August 2005 FILENAME: FIGURES-SECTION-GC04-04.dwg	FIGURE 9

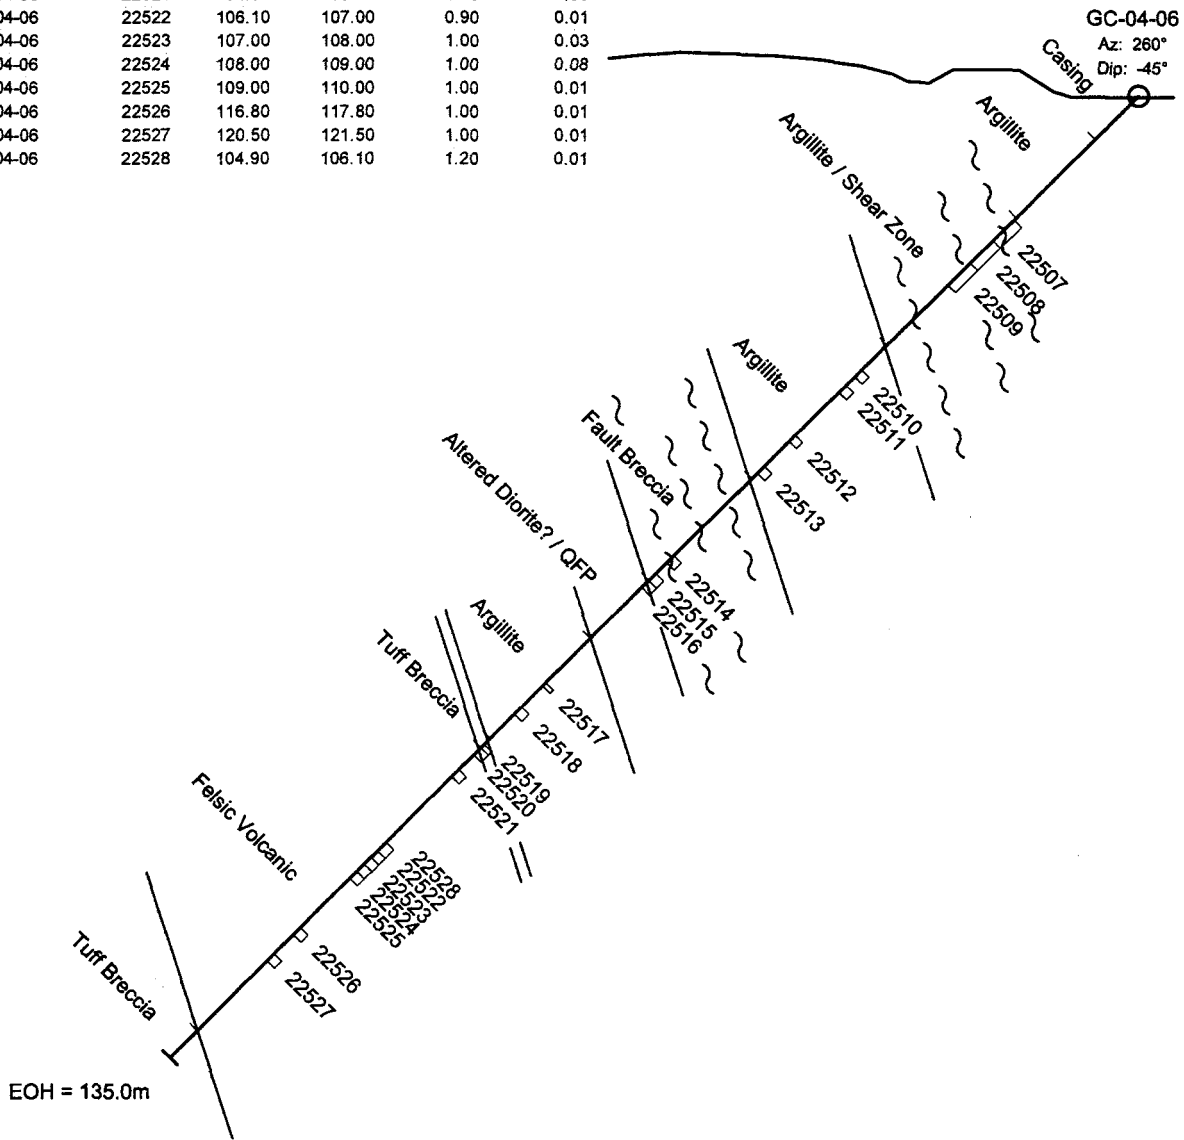
DDH	Sample No	From	To	Interval	Au g/t
GC04-05	22529	17.1	18.1	1.00	0.02
GC04-05	22530	28.57	29.57	1.00	0.01
GC04-05	22531	64.75	65.75	1.00	0.01
GC04-05	22532	73.25	73.75	0.50	0.01
GC04-05	22533	89.05	90.05	1.00	0.01
GC04-05	22534	68	68.5	0.50	0.01



EOH = 148.4m

NAVASOTA RESOURCES LTD.	
GOLD CREEK PROPERTY	
SECTION GC-04-05	
SCALE: 0 10 20 30 40m	
DRAWN BY: jfw DATE: August 2005 FILENAME: FIGURE10-SECTION-GC04-05.dwg	FIGURE 10

DDH	Sample No	From	To	Interval	Au g/t
GC04-06	22507	17.40	20.40	3.00	0.02
GC04-06	22508	20.40	23.50	3.10	0.03
GC04-06	22509	23.50	26.60	3.10	0.03
GC04-06	22510	38.60	39.60	1.00	0.04
GC04-06	22511	40.80	41.80	1.00	0.02
GC04-06	22512	47.85	48.70	0.85	0.01
GC04-06	22513	52.20	53.20	1.00	0.06
GC04-06	22514	64.80	65.80	1.00	0.04
GC04-06	22515	67.30	68.30	1.00	0.02
GC04-06	22516	68.30	69.30	1.00	0.03
GC04-06	22517	82.65	83.10	0.45	0.65
GC04-06	22518	86.00	87.00	1.00	0.96
GC04-06	22519	91.25	91.70	0.45	0.02
GC04-06	22520	91.70	92.70	1.00	0.03
GC04-06	22521	94.80	95.80	1.00	0.03
GC04-06	22522	106.10	107.00	0.90	0.01
GC04-06	22523	107.00	108.00	1.00	0.03
GC04-06	22524	108.00	109.00	1.00	0.08
GC04-06	22525	109.00	110.00	1.00	0.01
GC04-06	22526	116.80	117.80	1.00	0.01
GC04-06	22527	120.50	121.50	1.00	0.01
GC04-06	22528	104.90	106.10	1.20	0.01



NAVASOTA RESOURCES LTD.	
GOLD CREEK PROPERTY	
SECTION GC-04-06	
SCALE: 0 10 20 30 40m	
DRAWN BY: dhw DATE: August 2005 FILENAME: FIGURE11-SECTION-GC04-06.dwg	FIGURE 11

Appendix 5
Diamond Drill Logs

HOLE NUMBER:	GC-04-01	LOGGED BY:	R. Whiteaker	DOWNHOLE SURVEY		
PROJECT:	GOLD CREEK	DATE :	December 2004	DEPTH	AZIMUTH	DIP
NORTHING:	5689963	DRILLED BY:	Frontier Drilling	COLLAR	068 deg	-45 deg
EASTING:	262416	TOTAL DEPTH:	148.5m			

LITHOLOGY			STRUCTURE & MINERALIZATION			SAMPLING				
FROM (m)	TO (m)	DESCRIPTION	FROM (m)	TO (m)	DESCRIPTION	SAMPLE #	FROM	TO	INT.	AU
							m	m	m	g/t
0m	6.1m	CASING Casing								
6.1m	148.5m	ARGILLITE Medium to dark-grey, to locally black, fine-grained pyritiferous argillite with phyllitic weakly schistose foliation/textures (unit is intermediate between argillite and phyllite). Non-magnetic. Commonly crenulated with a silky foliation/cleavage. Relic bedding=banded appearance. Alternating lighter grey and darker grey layers, 2mm-10cm thick (average) light-grey beds 5-10 per metre, approximately 35 degrees to 40 degrees, 50 degrees to 30 degrees to CA, commonly foliated/deformed. Pyrite porphyroclasts (and andalusite?) approximately 2-8mm in diameter throughout. Micaceous element to unit. Limonite-oxide staining on fractures in rock mass to approximately 18m (after pyrite). Alternating lighter and dark grey layers of unit approximately 40 degrees to 50 degrees and 30 degrees to CA. Unit is well broken and/or crumbled to approximately 14.6m (probably surficial weathering/fracturing). Note: the thinner, light-grey layers/bands in unit contain majority of pyrite grains (medium to coarse, cubic, locally with a golden lustre – possibly cpy or pyrite tarnish/oxide?). Total pyrite approximately 1-3% overall as spot, clusters and coarse masses. Unit a lower grade, regionally metamorphosed mudstone, siltstone. Sooty, carbonaceous component. Pelitic origin? Relic mineralogy (andalusite?) porphyroclasts. Quartz veins/veinlets throughout hole, 60 degrees to 70 degrees, 40 degrees and 80 degrees to CA, 3mm to 4cm wide, irregularly spaced, locally with patchy cream-coloured feldspar (?) and/or trace fine pyrite. Quartz veins locally brecciated/sheared to well-broken. Fractures: approximately 5-8/m to 75.0m and 15-25/m downsection of 75.0m. Note: from approximately 30.5m light and dark grey layers/horizons commonly display 'soft' deformation and brecciation – i.e. bands foliated, bent/twisted and segmented as well as with smaller quartz veins locally (wider quartz veins cross-cut this deformation approximately 60 degrees to 70 degrees to CA).			1-3% pyrite	22588	23.50	25.00	1.50	<0.03

LITHOLOGY		STRUCTURE & MINERALIZATION			SAMPLING				
					SAMPLE #	FROM	TO	INT.	AU
	<p>40.26-40.41: White quartz vein at 10-15 degrees to CA, minimal tan ankerite.</p> <p>48.79-49.00: Top of fault zone, clay gouge – graphite. @48.9m: Fault approximately 10cm wide, 65 to 70 degrees to CA, black to dark-grey with milled very fine pyrite (+/- cpy??).</p> <p>49.00-49.50: Fractured white quartz vein, minimal tan ankerite. Lower contact at 10-15 degrees to CA; graphite slip.</p> <p>49.1m, 57.3: Brecciated/broken quartz vein, approximately 40cm wide with trace pyrite (sampled for assay). Note: @49.5m trace grains of galena within a sampled quartz vein.</p> <p>51.3-51.80: Quartz-ankerite stockwork, silicified zone; minimal pyrite veinlets up to 4cm thick.</p> <p>57.27-57.67: Fractured white quartz vein, as before.</p> <p>57.87-58.00: Fractured white quartz vein, as before.</p> <p>59.7-60.1: Fault gouge approximately 50 degrees to 60 degrees to CA, thick dark grey gouge with milled and smeared fine pyrite throughout. Some brecciated quartz veins. <u>Very</u> weak carbonate.</p> <p>68.40: Strong layers of siltstone at 10-15 degrees to CA. S2 dips opposite direction. Local section of 'spotted' argillite; carbonate-alteration?</p> <p>74.3:→Dramatic increase in fracture density increases to E.O.H. <u>Note:</u> from approximately 74.5m there is an increase in the intensity and frequency of 'deformation'/foliation and segmented brecciation of the light and dark units of the hole. As well, fracturing of rock increases with numerous faults and breccia zones (see below). Cross cutting quartz +/- feldspar +/- pyrite veins also foliated/brecciated.</p> <p>76.2-79.3m, 87.2-88.7m: Fault brecciated rock; well fractured/broken with localized crushed slips and narrow gouge – no recordable CA (possibly approximately 50 degrees to 60 degrees to CA?). <u>Note:</u> Downsection of 90.0m quartz veins mainly 60 to 70 degrees to CA, except where brecciated approximately 20 to 35 degrees to CA, irregular and commonly segmented.</p> <p>78.33-79.15: Rubbly, moderate gougy fault zone.</p> <p>79.15-79.35: Irregular white quartz-carbonate vein, no ankerite. Far less pyrite through most of hole, including veins.</p> <p>79.79-79.89: 2cm white quartz vein.</p>								
					22589	48.60	50.10	1.50	<0.03
					22590	56.70	58.70	2.00	0.06
					22591	78.70	80.70	2.00	0.03

LITHOLOGY		STRUCTURE & MINERALIZATION			SAMPLING				
					SAMPLE #	FROM	TO	INT.	AU
	<p>80.88-81.43: Stockwork veinlets of quartz – carbonate, minor pyrite; many different orientations.</p> <p>83.98-84.43: Another zone of stockwork silicification.</p> <p>83.71-83.63: Minor white quartz vein, sheared, graphitic slips. Narrow quartz veinlets, silicified zones continue, relatively weak.</p> <p>93.87-94.47: Quartz vein at 10% to CA and silicified stockwork zone.</p> <p>102.72-105.77: 1.5m recovered.</p> <p>105.3-106.1m: Brecciated and broken quartz +/- feldspar +/- pyrite vein, tectonically brecciated approximately 25 degrees to CA (assay sample); sheared @ top approximately 40 degrees to CA.</p> <p>105.97-106.67: Rubbly fractured white quartz vein.</p> <p>107.27-107.57 Rubbly fractured white quartz vein.</p> <p>112.78:→Increasing rubbly with dark graphitic look very minor pyrite, occasional cm-size quartz veinlets.</p> <p>113.4-114.9: Strong fault brecciation with slips and gouge approximately 60 to 70 degrees and 30 to 40 degrees to CA. Milled and crushed pyrite throughout. 0% RQD.</p> <p>@121.7: Fault approximately 50 to 60 degrees to CA, 5cm wide.</p> <p>@131.7, 136.3, 137.0: Quartz (+/- feldspar +/- trace pyrite) veins approximately 45 degrees to 50 degrees to CA, approximately 3-7cm wide.</p> <p>136.4 to E.O.H.: Unit well broken, shattered with localized shears/brxn. 0% R.Q.D. Possible slip/shear planes approximately 30 to 40 degrees to CA. Local crushed and dusty gouge approximately 2-4cm wide (no CA).</p> <p>@136.m and 136.9: Strong gouge approximately to CA, faults, 2-3cm wide.</p>								
					22592	85.50	86.50	1.00	<0.03
					22593	93.80	94.80	1.00	<0.03
					22594	105.60	108.60	3.00	0.04
					22595	136.90	138.90	2.00	0.04
					22596	146.90	147.90	1.00	<0.03
148.5	End Of Hole.								

HOLE NUMBER:	GC-04-02	LOGGED BY:	R. Whiteaker	DOWNHOLE SURVEY		
PROJECT:	GOLD CREEK	DATE :	December 2004	DEPTH	AZIMUTH	DIP
NORTHING:	5689687	DRILLED BY:	Frontier Drilling	COLLAR	068 deg	-45 deg
EASTING:	292494	TOTAL DEPTH:	151.7m			

LITHOLOGY			STRUCTURE & MINERALIZATION			SAMPLING				
FROM (m)	TO (m)	DESCRIPTION	FROM (m)	TO (m)	DESCRIPTION	SAMPLE #	FROM	TO	INT.	AU
							m	m	m	g/t
0m	6.1m	CASING / OVERBURDEN								
6.1m	151.7m	<p>ARGILLITE-PHYLLITE Medium to dark grey/ black Argillite-Phyllite. Unit consistent throughout hole - *see GC-04-01 (first page of log)* for detailed description of rock lithology and characteristics.</p> <p>Light and darker grey beds/layers metamorphosed pelitic layers and Quartz +/- Pyrite +/- Feldspar veins throughout: 60 degrees to 70 degrees and 10 to 20 degrees to CA; quartz veins ~ 5mm-1.5cm wide, locally up to 8cm wide. Note: very weak HCl acid reaction associated with quartz veining (carb. poor). Quartz veining commonly deformed, folded and segmented irregular in orientation within core. Quartz veins cross cut all units down hole.</p> <p>6.1m-7.1m: Lim-oxidized rock/ fractures (weak to moderate). <u>Note:</u> Pyrite cubes are beaded and clustered dominant within lighter-grey sub-units/ bands in hole, 1 -20cm thick, laminar to well deformed/ folded). Deformation structures/ features common between and within boundaries of light-grey and dark-grey sub-units.</p> <p><u>Fractures:</u> Approximately 5-10 per metre (average), 20 degrees to 25 degrees, 35 degrees to 40 degrees and 55 degrees to 65 degrees to C.A.</p> <p>43.3-43.8m: Fault breccia/gouge, approximately 50 degrees to C.A. Dark grey to black, soft and crumbly, some milled pyrite, weak carbonate component.</p> <p>112.0-132.0m: Zone of increasing brecciation and fracturing with strong localized fault breccia gouge @ 105.5- 106.7m and 110.4-111.4m (carbonaceous, weak carbonate, 55 to 65 degrees and 40 degrees to C.A. slip surfaces, fine pyrite crushed and milled throughout, brecciated fragments of argillite and phyllite.</p> <p>@136.5m: 15cm wide fault breccia approximately 50 degrees to C.A. Crushed, dry and crumbled. <u>Note:</u> sample # 22583: a quartz vein, 1 cm wide, 20 degrees to C.A. with a 2mm in diameter silver - grey, soft metallic sx- Molybdenite.</p>			+/-pyrite					
					pyrite	22579	33.40	34.90	1.50	0.13
					Tr pyrite	22580	43.30	44.80	1.50	<0.03
					pyrite	22581	70.50	72.00	1.50	0.03
						22582	87.90	88.90	1.00	0.12
						22583	90.70	91.70	1.00	0.05
						22584	104.90	105.90	1.00	<0.03
					molybdenite	22585	114.80	116.30	1.50	0.05
						22586	133.40	134.40	1.00	0.04
						22587	150.20	151.20	1.00	0.03
		151.7 m: EOH								

HOLE NUMBER:	DDH-04-03	LOGGED BY:	R. Whiteaker	DOWNHOLE SURVEY		
PROJECT:	GOLD CREEK	DATE :	December 2004	DEPTH	AZIMUTH	DIP
NORTHING:	5690152	DRILLED BY:	Frontier Drilling	COLLAR	248 deg	-45 deg
EASTING:	292355	TOTAL DEPTH:	148.5 m			

LITHOLOGY			STRUCTURE & MINERALIZATION			SAMPLING				
FROM (m)	TO (m)	DESCRIPTION	FROM (m)	TO (m)	DESCRIPTION	SAMPLE #	FROM	TO	INT.	AU
							m	m	m	g/t
0m	6.1m	CASING/OVERBURDEN								
6.1m	148.5m	<p>ARGILLITE-PHYLLITE</p> <p>Fine-grained argillite-phyllite, non-magnetic, alternating dark and lighter grey colour due to relic bedding/layers of pelitic material/siltstones/mudstones. CA angle of metamorphosed bedding variable throughout but typically 30 degrees, 40 degrees >20 degrees, 50 to 60 degrees to CA. Darker grey-black argillite-phyllitic sub-units per metre, 0.5cm to 20cm wide (range); units commonly deformed, foliated and/or brecciated into discontinuous and segmented bands and clustered zones. Good cleavage visible in cross section.</p> <p>Local quartz, +/-feldspar, +/- pyrite veins throughout, approximately 3-30cm wide, 35, 75, and 55 degrees to CA, white with creamy- yellow patches, pyrite is trace as fine dissemination on fracture planes. Widest quartz veins noted below. Unit contains approximately 5-12 fractures per metre @ approximately 50 degrees, 30 degrees and 20 degrees to CA. Where brecciated/ crushed fracturing greater- see below. Fracture planes shiny, silky due to phyllitic foliation and mineralogy. Unit displays crenulation. Pyrite cubes as random coarse grains and as cluster/beaded along relic bedding planes. Pyrite more common within or adjacent to the light-grey sub- unit.</p> <p>13.71: 25cm wide quartz-feldspar +/- pyrite vein approximately 35 degrees to CA. Sample taken for assay. Note: Very fine metallic-grey sx with pyrite in vein-possibly sphalerite?</p> <p>27.6: 40cm wide quartz veins as described above cross-cutting @ approximately 60 degrees to CA. Sampled for assay along with pyrite- rich wallrock.</p> <p>38.71-40.85, 49.1-53.35: Sections of brecciated dark and light-grey argillite/ phyllite. No tectonic shearing or gouge-possibly a slumping/ soft deformation event. Cross cut by quartz veins approximately 50 degrees to CA.</p> <p>@53.9: Quartz vein approximately 35cm wide, 79 degrees to CA, trace fine pyrite along contact with argillite/phyllitic unit, and within vein. Assay sample taken.</p> <p>57.0 - 75.3: Argillite/ Phyllitic unit very tough, poorly fractured with</p>			Pyrite	22597	12.90	13.90	1.00	<0.03
						22598	26.50	28.50	2.00	<0.03
						22599	53.40	54.90	1.50	<0.03

LITHOLOGY		STRUCTURE & MINERALIZATION			SAMPLING				
					SAMPLE #	FROM	TO	INT.	AU
	<p>layers/beds oriented approximately 40 degrees, 50 degrees and 70 degrees to CA lending a consistent striped/banded appearance to unit.</p> <p>@ 82.6: Quartz vein, brecciated/foliated approximately 30 degrees to CA, 4cm wide.</p> <p>@ 83.21: Quartz vein, 5cm wide, un-brecciated approximately 70 degrees to CA (both veins sampled for assays). Trace fine pyrite.</p> <p>84.58-91.44: Zone of well deformed brecciated dark and light-grey argillite/phyllitic units approximately 40 degrees to 50 degrees to CA. Possible pre-tectonic deformation. Beds sheared and segmented into irregular lens shaped fragments approximately 2mm-2cm long (flattened and stretched) commonly up to 5-8cm long. Pyrite grains also sheared along with main unit.</p> <p>Note @ 86.3, 92.7: 4-8cm wide faults approximately 60 to 70 degrees to CA, milled pyrite in brecciated rock/ gouge.</p> <p>101.3-102.4: <u>Dark</u> grey to black "sooty" clayey-sand. Weak gouge component, no record able CA angle or slip planes. Very fine pyrite milled throughout.</p> <p>114.63 -115.24: Brecciated quartz veins less than 1cm wide with coarse vuggy quartz crystals intergrown with pyrite where fractures are opened. Sample for assay taken.</p> <p>123.2-123.8: 40cm wide quartz vein approximately 60 degrees to 70 degrees to CA, trace pyrite locally, vuggy. Sample for assay collected.</p> <p>Note: From approximately 109.0m to E.O.H.: General increase in volume of coarse cubic pyrite randomly distributed throughout unit.</p> <p>133.7-134.1: Fault brecciated and crushed argillite unit approximately 25 degrees to 30 degrees to CA. 0% RQD.</p> <p>@ 144.5: 50cm wide fault brecciated/shear zone approximately 20 to 25 degrees to CA. Unit well broken-crushed. Milled pyrite.</p>				22600	82.00	83.50	1.50	0.08
					22501	85.40	86.40	1.00	0.04
					22502	100.50	101.50	1.00	0.04
					22503	106.30	107.30	1.00	0.04
					22504	114.60	115.60	1.00	0.07
					22505	123.10	124.10	1.00	0.05
					22506	140.20	141.70	1.50	<0.03
148.5m	End Of Hole.								

HOLE NUMBER:	GC-04-04	LOGGED BY:	R. Whiteaker	DOWNHOLE SURVEY		
PROJECT:	GOLD CREEK	DATE :	December 2004	DEPTH	AZIMUTH	DIP
NORTHING:	5690533	DRILLED BY:	Frontier Drilling	COLLAR	248 deg	-45 deg
EASTING:	292214	TOTAL DEPTH:	151.5 m			

LITHOLOGY			STRUCTURE & MINERALIZATION			SAMPLING				
FROM (m)	TO (m)	DESCRIPTION	FROM (m)	TO (m)	DESCRIPTION	SAMPLE #	FROM	TO	INT.	AU
							m	m	m	g/t
0m	3.1m	CASING/OVERBURDEN								
3.1m	151.5m	<p>ARGILLITE-PHYLLITE Medium to dark-grey/black argillite-phyllitic unit (consistent lithology to E.O.H.). Weak schistose textures visible. Banded appearance (*see DDH-04-01 for identical description of this unit). Generally a competent, tough rock, locally brecciated (see below).</p> <p>Fractures: Approximately 5-8 per metre (average), 25 to 30 degrees and 55 to 60 degrees to CA, commonly with a shiney black carbonaceous coating.</p> <p>3.1-6.4: Limonite oxide stained rock/fractures (after pyrite)</p> <p>17.4: Fault gouge, well brecciated – no CA recordable, 10 cm wide.</p> <p>34.1-34.35: 4cm white to pale grey quartz vein @ 20 degrees to CA. Local orthogonal tension cracks. Tan carbonate (ankerite) and white calcite (5% blebby pyrite throughout, finer and weaker in centre in vein.</p> <p>48.85-49.15: Weak quartz-calcite stockwork, also approximately 20 degrees to CA. Large cubic pyrite clusters.</p> <p>66.36-66.55: White quartz vein; moderate fractured. Sharp upper contact approximately 30 degrees to CA, pyrite and tan cb. Graphitic slip at 20 degrees to CA.</p> <p>66.95-67.13: Similar white quartz vein, minor tan carbonate. Minor argillite clasts. Pyrite along lower contact @ 45-50 degrees to CA.</p> <p>72.07-72.47: White bull quartz, upper contact 60-70 degrees to CA; tan cb. Lower contact @ 75 degrees to CA on graphitic slip, min (1cm) quartz calcite veinlet cuts S2 (S2 @ 75).</p> <p>74.63-74.68: 2x2 cm bands of clustered-cubic pyrite @ 60-65 degrees to CA.</p> <p>81.96-82.4: Fractured white bull quartz vein; min ankerite. Lower contact @</p>								
					5% pyrite	22571	34.20	35.20	1.00	0.39
					pyrite					
					pyrite	22572	44.90	45.90	1.00	0.03
					pyrite					
					pyrite	22573	66.10	67.60	1.50	0.03
						22574	72.00	73.00	1.00	<0.03

LITHOLOGY		STRUCTURE & MINERALIZATION			SAMPLING				
					SAMPLE #	FROM	TO	INT.	AU
	<p>80 degrees to CA.</p> <p>84.62-84.77: 2 white quartz veins, 2 cm and 1.5 cm, steep to CA is strong ankerite; both cut older 1 cm grey dendritic quartz cb veinlet. @ low angle to CA (10 degrees).</p> <p>@45.3, 67.4, 72.4, 82.2, 103.4, 117.0m: White quartz veins transecting unit. Locally containing cream-coloured feldspar (?). Cross cutting argillite/phyllite approximately 20 degrees, 35 degrees to 40 degrees and 60 degrees to 70 degrees to CA, approximately 10-35 cm wide, trace pyrite within veins and along envelope locally. No other cross cut recorded. Note: smaller quartz veins observed throughout hole, <1-5cm wide, same CA orientation and characteristics as described above; more very weak carbonate (very weak HCl reaction) locally.</p> <p>85.52-85.57: 5 cm white quartz vein cut by 6 cm clay fault zone @ 20 to 30 degrees to CA. Several cm size white quartz-calcite veinlets at a variety of orientations 1-2 per 5' length.</p> <p>95.85-96.18: White quartz with tan ankerite (20%). Lower contact @ 55 degrees to CA (upper contact likely faulted).</p> <p>99.72-99.87: White quartz vein, minimal pyrite, pale calcite. Upper contact @ 35 degrees to CA.</p> <p>103.4-103.70: White quartz vein with minimal ankerite. Lower contact @ 30 degrees to CA.</p> <p>112.16-112.24: White quartz ankerite (as above). Lower contact @ 60 degrees to CA.</p> <p>116.84-116.98: White quartz ankerite vein. Lower contact @ 70 degrees to CA.</p> <p>117.89-118.03: Silicified zone, weak stockwork quartz calcite veining grey to white veinlets, flooding into host; @ 60-70 degrees to CA.</p> <p>139.94-139.99: 5x2 cm clast of pale grey silt with pyrite.</p> <p>140.0-151.5m: Increasing fracturing, brecciation and deformation/foliation of metamorphosed beds/sub-units (approximately to 45 degrees to 50 degrees to CA). Tectonically brecciated with rounded to sub-angular fragments of light-grey pyritiferous argillite/phyllite elongated approximately 45 to 50 degrees to CA in a dark-grey to black matrix of primary unit (argillaceous phyllite). Local coarse clustering of pyrite into masses 5-10cm wide. Brecciated fragments approximately 2mm-2cm in length, locally up to 10-15cm. No carbonate HCl acid reaction.</p> <p>141.64-141.70: 7x7 cm layer or clast →both strongly pyritized, up to 50%.</p>			Tr pyrite					
					22575	81.70	82.70	1.00	<0.03
					22576	103.00	104.00	1.00	<0.03
					22577	116.60	117.60	1.00	0.05
				pyrite					

LITHOLOGY			STRUCTURE & MINERALIZATION			SAMPLING				
						SAMPLE #	FROM	TO	INT.	AU
		144.18-145.59: Deformation brecciated, variable intensity with cm-size pale grey silty clasts, elongated to rounded. Variable brecciated continues to EOH.			pyrite					
						22578	141.00	142.00	1.00	0.35
	151.5m	End Of Hole.								

HOLE NUMBER:	GC-04-05	LOGGED BY:	C. Wild, R. Wild	DOWNHOLE SURVEY		
PROJECT:	GOLD CREEK	DATE:	Feb. 19, 2005	DEPTH	AZIMUTH	DIP
NORTHING:	5690711	DRILLED BY:	Frontier Drilling	COLLAR	248 deg	-45 deg
EASTING:	291706	TOTAL DEPTH:	148.44m			

LITHOLOGY			STRUCTURE & MINERALIZATION			SAMPLING				
FROM (m)	TO (m)	DESCRIPTION	FROM (m)	TO (m)	DESCRIPTION	SAMPLE #	FROM m	TO m	INT. m	AU g/t
0m	9.4m	CASING			trace pyrite					
9.4m	11.3m	DIORITE Coarse-grained, medium green-grey, equigranular plagioclase and pyroxene, non-magnetic, calcite on fractures, rare fine grained pyrite. Weak sericite and chlorite alteration, hard, weakly fractured, 100% recovery.								
11.6m	12.3m	GABBRO Fine-medium-grained, medium-grey, weakly porphyritic with 10% patchy green chlorite-phenos. Sharp contacts, no chill but quartz-calcite veinlets (2mm) @45 degrees to CA. Ser, chlorite Alteration 11.7-11.9: White quartz (calcite) vein, 5 cm thick (true) @25 degrees to CA.								
12.3m	27.6m	DIORITE Coarse-grained diorite, as above (9.4-11.3) Sericite, chlorite alteration 20.5 1cm quartz-calcite vein @ 30 degrees to CA. 27.4-27.9: Lower contact on sericite-calcite-shear @ approximately 20 degrees to CA over 40-50cm core length. Several sub parallel fractures on both sides of contact.			trace pyrite	22529	17.1	18.1	1.00	0.02
27.6m	148.44	GABBRO-DIORITE Fine-grained diorite-gabbro, as above (11.3-12.3). Very uniform, homogeneous, hard, close to 100% recovery, weakly fractured (>75% RQD). May gradually get more chlorite toward bottom. Occasional quartz-calcite veins. Sericite, chlorite, carbonate alteration 34.5: 4cm quartz-calcite vein @ 40 degrees to CA. 52.25: 2cm quartz-calcite vein @ 40 degrees to CA.				22530	28.57	29.57	1.00	0.01

LITHOLOGY		STRUCTURE & MINERALIZATION			SAMPLING				
					SAMPLE #	FROM	TO	INT.	AU
	<p>49.5-57.0: 7 other veinlets approximately 1cm thick.</p> <p>65.3: significant cubic pyrite.</p> <p>65.6 hematite on slickenside surface @ 55 degrees to CA.</p> <p>68.0-68.5: Weak quartz-calcite stockwork with diffuse quartz-rich 5-10mm veinlets @ 45 to CA and more calcite-rich fracture irregular but parallel to CA.</p> <p>73.3-73.5: Weakly foliated quartz quartz-calcite stockwork to vein breccia @ 30 to 40 degrees to CA, calcite-rich.</p> <p>89.4-89.8: Quartz-calcite-epidote stockwork zone – wispy epidote with quartz almost chalcedonic.</p> <p>95.9: Chlorite-fracture, polished but slipped @ 40 degrees to CA.</p> <p>98.0: 3.5 cm fine-grained chalcedonic-quartz-calcite-epidote vein @ 65 degrees to CA.</p> <p>110 More chloritic, darker. Remains virtually non-magnetic. Chlorite-calcite common. Chlorite-sericite on fractures</p> <p>118.3: 3 cm chalcedonic quartz calcite-epidote vein @ 40 degrees to CA (35-45 degrees).</p> <p>119.3: 1.5cm quartz-calcite-epidote vein with line of pyrite @ 20 degrees to CA. Pyrite is relatively coarse-grained and cubic.</p> <p>128.6: Wispy epidote over 5cm @ 45 degrees to CA.</p> <p>137.85: 2.5 cm quartz-calcite-chlorite veinlet; sericitic shear on footwall side @ 20 degrees to CA (parallel to vein).</p> <p>130.40: 2 quartz-carbonate-chlorite veinlets, 1.5 and 1.0 cm thick, @ 35 and 65 degrees to CA, second is more calcite-rich, fractured on lower contact and may be slightly younger.</p> <p>130.25: Wispy epidote associated with more diffuse quartz (calcite) veinlets @ 35 degrees to CA.</p>								
					22531	64.75	65.75	1.00	0.01
					22532	73.25	73.75	0.50	0.01
					22533	89.05	90.05	1.0	0.00
					22534	68.00	68.50	0.50	0.01
148.44m	End Of Hole.								

HOLE NUMBER:	GC-04-06	LOGGED BY:	C. Wild, R. Wild	DOWNHOLE SURVEY		
PROJECT:	GOLD CREEK	DATE :	February 2005	DEPTH	AZIMUTH	DIP
NORTHING:	5692755	DRILLED BY:	Frontier Drilling	COLLAR	260 deg	-45 deg
EASTING:	291435	TOTAL DEPTH:	135.0 m			

LITHOLOGY			STRUCTURE & MINERALIZATION			SAMPLING				
FROM (m)	TO (m)	DESCRIPTION	FROM (m)	TO (m)	DESCRIPTION	SAMPLE #	FROM	TO	INT.	AU
							m	m	m	g/t
0.00m	6.10m	CASING – no recovery								
6.10m	17.1m	ARGILLITE Dark grey and black fine-grained moderately foliated, contorted banding. Blebby pyrite, aligned along foliation, also finely disseminated. Chlorite-carbonate-pyrite along fractures. Looking more brecciated toward end of interval. Minimum carbonate alteration. Chlorite-carbonate-pyrite alteration. 6.1-11.3 Decr orange oxidation on fractures. Only very minor quartz-carbonate veinlets. S2 approximately 45 degrees to CA.			2% pyrite.					
17.1m	35.1m	ARGILLITE/SHEAR ZONE Quartz-calcite alteration. 17.1-20.4 White to grey quartz, minimal calcite stockwork in fractured rubbly argillite. Fine-grained cubes of pyrite come along veinlet selvages. Poor recovery. 20.4-23.4 Weak stockwork in highly sheared argillite. Very poor recovery. 23.4-26.5 Moderate quartz (calcite) stockwork, as 17.1-20.4. Again very poor recovery. Some shearing likely postdates stockwork. 26.5 Increase graphite on slips and fractures. 29.0-30.0 Fault Fine dark gouge with fine pyrite. 30.0-35.1 Improved recovery, back to graphitic argillite, quite deformed with occasional pale grey, cm-size angular clasts. Fine-grained and blebby S2 parallel pyrite clasts.			1% pyrite. <1% pyrite. 1% pyrite. <1% pyrite. 1% pyrite.	22507 22508 22509	17.40 20.40 23.50	20.40 23.50 26.60	3.00 3.10 3.10	0.02 0.02 0.02
35.1m	53.95m	ARGILLITE Medium to dark grey, fine-grained, contorted to moderately brecciated. 35.1-38.1 Moderate ankerite, yellow-brown colour with relative strong fine-grained to blebby pyrite; fractured cubic pyrite. Possibly weakly silicified. 37.8 3-4 cm white quartz vein @ 50-60 degrees to CA. Patchy yellowish			2% pyrite 5% pyrite					

LITHOLOGY			STRUCTURE & MINERALIZATION			SAMPLING				
						SAMPLE #	FROM	TO	INT.	AU
		<p>ankerite. 5mm cubic blebs of pyrite</p> <p>38.1-42.0 Silicified zone contact @ 70 degrees to CA. Moderate brecciated, fine wispy pyrite, concentrated blebs.</p> <p>41.0-41.2 White quartz vein with patchy ankerite Upper contact @ 50 degrees to CA. Late, cuts pale silic unit.</p> <p>44.7-45.4 Pyrite-rich zones, bands of close to massive pyrite. Also, clasts of silic-pyrite argillite in darker pyritic argillite-angular, 2-3cm (45.1m).</p> <p>47.0-47.3 Pale grey silicified zone, breccia. Part of matrix has fine sericite phenos (1mm).</p> <p>47.85-48.7 70 degrees to CA (upper contact), 60 to 70 degrees to CA (lower contact). White bull quartz vein, clasts of argillite near contacts (host rock), weak min patchy ankerite near contacts.</p> <p>48.7 Weakly silicified, variably brecciated, graphitic slips.</p> <p>52.4-52.5 Silicified breccia interval, moderate to strong quartz vein stockwork, minimal very fine-grained pyrite.</p>			<p>15-20% pyrite</p> <p>3-5%</p> <p><1% pyrite</p> <p>2% pyrite</p>	<p>22510</p> <p>22511</p> <p>22512</p> <p>22513</p>	<p>38.60</p> <p>40.80</p> <p>47.85</p> <p>52.20</p>	<p>39.60</p> <p>41.80</p> <p>48.70</p> <p>53.20</p>	<p>1.00</p> <p>1.00</p> <p>0.85</p> <p>1.00</p>	<p>0.03</p> <p>0.02</p> <p>0.01</p> <p>0.06</p>
53.95m	68.3m	<p>FAULT BRECCIA Coarse, polymictic matrix-supported argillite-dominated, dark grey. Clasts of silicified and pyritic argillite in black argillite matrix. Silic alteration.</p>			2-3% pyrite	<p>22514</p> <p>22515</p>	<p>64.80</p> <p>67.30</p>	<p>65.80</p> <p>68.30</p>	<p>1.00</p> <p>1.00</p>	<p>0.04</p> <p>0.02</p>
68.3m	76.4m	<p>ALTERED DIORITE (?) QFP Pale greenish grey, moderately brecciated, healed. Strong fault breccia with 10% argillite clasts near top with argillite decreasing, clast size increasing. Alteration varies from moderate silic to strong ser. Wide range of clasts sizes up to several cm; several mm-size argillite fragments, quartz-eyes, felsic (dacite or rhyolite) fragments – poorly sorted. Generally, hard, competent, weak fractures. Silicified-sericite-pyrite alteration</p> <p>68.3-72.0 Pale grey, blocky, clasts supported, strong sericite matrix.</p> <p>72.0-73.8 Medium-darker grey, medium-grained with occasional blocks – looks possible volcanoclastic. Weaker sericite alteration, occasional quartz veinlets.</p> <p>73.8-74.2 Interval or block of pale grey very brecciated, as 68.3-72.0m. Pyrite most associated along chlorite fracture.</p> <p>74.2-74.8 Medium-darker grey interval as before.</p> <p>74.8-75.05 Pale grey, large angle clasts, strong sericite matrix, some in clasts.</p>			<p>2% pyrite</p> <p>1%</p> <p><1%</p> <p>trace</p> <p><1%</p> <p><1%</p>	<p>22516</p>	<p>68.3</p>	<p>69.3</p>	<p>1.00</p>	<p>0.02</p>

LITHOLOGY			STRUCTURE & MINERALIZATION			SAMPLING				
						SAMPLE #	FROM	TO	INT.	AU
		75.05-76.4 Sharp transition to pale grey, blocky (1-2cm), higher pyrite content.			3-5% pyrite					
76.4m	90.4m	<p>ARGILLITE Dark grey, with interlayered medium grey bands, fine-grained. Pyrite bands and disseminated.</p> <p>79.2 3cm quartz vein, trace ankerite, coarse pyrite cube across contact; @ 80% to CA. Silicified</p> <p>82.7-83.1 White quartz vein, minimal ankerite, incorporated black argillite with cubic pyrite.</p> <p>86.4-86.5 White quartz vein, occasional vugs with 1mm quartz crystals, pyrite minimal ankerite.</p>			2% pyrite	22517	82.65	83.10	.045	0.645
						22518	86.00	87.00	1.00	0.960
90.4m	91.7m	<p>TUFF BRECCIA Blocky, pale grey, siliceous unit, same as pale grey intervals 68.3-72.0m etc.</p>			1% pyrite	22519	91.25	91.70	0.45	0.01
91.7m	131.2m	<p>FELSIC VOLCANIC (Rhyolite/dacite breccia). Pale greenish grey, locally weakly banded to wispy with white fine-grained quartz veinlets siliceous intervals. Generally quite homogeneous. Silic, sericite alteration.</p> <p>95.2 Coarse grained pyrite, 3x6mm galena grain enclosed in pyrite, associated with quartz veining. In pale grey bands or quartz structures, these are tension cracks in-filled with dark grey sulphides and quartz – very fine. Also pale greenish sericite. Occasional pyrite cubes to 2mm. Locally spotted with pale green sericite likely replacing feld phenos, typically approximately 1mm.</p> <p>120.9-121.2 Well-developed fine breccia with sharp angular clasts in quartz matrix and disseminated to cubic pyrite.</p>			1% pyrite	22520	91.70	92.70	1.00	0.03
						22521	94.80	95.80	1.00	0.03
						22522	106.10	107.00	0.90	0.00
						22523	107.00	108.00	1.00	0.02
						22524	108.00	109.00	1.00	0.08
						22525	109.00	110.00	1.00	0.00
						22526	116.80	117.80	1.00	0.00
						22527	120.50	121.50	1.00	0.00
						22528	104.90	106.10	1.20	0.00
131.2m	135.0m	<p>TUFF BRECCIA Medium green-grey, blocky tuff breccia to tuff; texturally more variable than homogeneous interval. Occasional cm-size quartz veinlets, white and grey quartz. Silic-sericite alteration. Very similar to 68.3-76.4m.</p> <p>108.25-108.4: Quartz veining with coarse-grained pyrite, reddish sphalerite, galena</p> <p>Pyrite 10%, sphalerite trace-1% galena 1-2%. End Of Hole.</p>			Trace to 1% pyrite					

Appendix 6
Analytical Procedures
Certificates of Analysis

Analytical Procedure Assessment Report

GEOCHEMICAL GOLD ANALYSIS

Samples are catalogued and dried. Soils are prepared by sieving through an 80 mesh screen to obtain a minus 80 mesh fraction. Samples unable to produce adequate minus 80 mesh material are screened at a coarser fraction. These samples are flagged with the relevant mesh. Rock samples are 2 stage crushed to minus 10 mesh and a 250 gram subsample is pulverized on a ring mill pulverizer to -140 mesh. The subsample is rolled, homogenized and bagged in a prenumbered bag.

The sample is weighed to 30 grams and fused along with proper fluxing materials. The bead is digested in aqua regia and analyzed on an atomic absorption instrument. Over-range values for rocks are re-analyzed using gold assay methods.

Appropriate reference materials accompany the samples through the process allowing for quality control assessment. Results are entered and printed along with quality control data (repeats and standards). The data is faxed and/or mailed to the client.

Analytical Procedure Assessment Report

MULTI ELEMENT ICP ANALYSIS

Samples are catalogued and dried. Soil samples are screened to obtain a -80 mesh sample. Samples unable to produce adequate -80 mesh material are screened at a coarser fraction. These samples are flagged with the relevant mesh. Rock samples are 2 stage crushed to minus 10 mesh and pulverized on a ring mill pulverizer to minus 140 mesh, rolled and homogenized.

A 0.5 gram sample is digested with 3ml of a 3:1:2 (HCl:HN03:H2O) which contains beryllium which acts as an internal standard for 90 minutes in a water bath at 95°C. The sample is then diluted to 10ml with water. The sample is analyzed on a Jarrell Ash ICP unit.

Results are collated by computer and are printed along with accompanying quality control data (repeats and standards). Results are printed on a laser printer and are faxed and/or mailed to the client.

K:Methods/methicp

Analytical Procedure Assessment Report

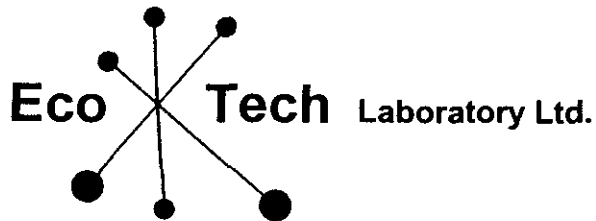
BASE METAL ASSAYS (Ag,Cu,Pb,Zn)

Samples are catalogued and dried. Rock samples are 2 stage crushed followed by pulverizing a 250 gram subsample. The subsample is rolled and homogenized and bagged in a prenumbered bag.

A suitable sample weight is digested with aqua regia. The sample is allowed to cool, bulked up to a suitable volume and analyzed by an atomic absorption instrument, to .01 % detection limit.

Appropriate certified reference materials accompany the samples through the process providing accurate quality control.

Result data is entered along with standards and repeat values and are faxed and/or mailed to the client.



ASSAYING
GEOCHEMISTRY
ANALYTICAL CHEMISTRY
ENVIRONMENTAL TESTING

10041 Dallas Drive, Kamloops, BC V2C 6T4
Phone (250) 573-5700 Fax (250) 573-4557
E-mail: info@ecotechlab.com
www.ecotechlab.com

CERTIFICATE OF ANALYSIS AK 2004-992

NAVASOTA RESOURCES
#207 141 VICTORIA STREET
KAMLOOPS, BC
V2C 1Z5

20-Aug-04

No. of samples received: 15
Sample type: Rock
Project #: Gold Creek
Shipment #: Not indicated
Samples submitted by: Royanna Wild

ET #.	Tag #	Au (ppb)	Pt (ppb)	Pd (ppb)
1	QV-04-001	<5		
2	QV-04-002	5		
3	QV-04-003	55		
4	QV-04-004	10		
5	QV-04-005	665		
6	QV-04-008	5		
7	GK-04-006	5		
8	GK-04-007	25	<5	<5
9	GK-04-009	>1000		
10	GK-04-010	75		
11	GK-04-011	15		
12	GK-04-012	15		
13	GK-04-013	30		
14	GK-04-014	<5		
15	GK-04-015	<5		

QC DATA:

Repeat:

1	QV-04-001	<5		
5	QV-04-005	650		

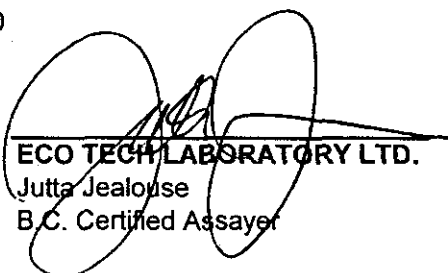
Resplit:

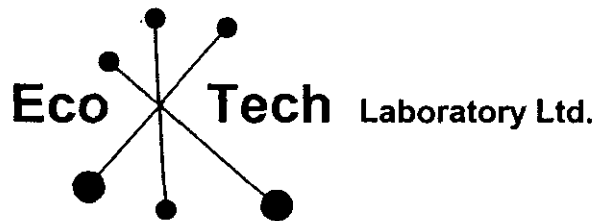
1	QV-04-001	<5		
---	-----------	----	--	--

Standard:

GEO'04		140		
--------	--	-----	--	--

JJ/jm
XLS/04


ECO TECH LABORATORY LTD.
Jutta Jealous
B.C. Certified Assayer



ASSAYING
 GEOCHEMISTRY
 ANALYTICAL CHEMISTRY
 ENVIRONMENTAL TESTING

10041 Dallas Drive, Kamloops, BC V2C 6T4
 Phone (250) 573-5700 Fax (250) 573-4557
 E-mail: info@ecotechlab.com
 www.ecotechlab.com

CERTIFICATE OF ASSAY AK 2004-992

NAVASOTA RESOURCES
 #207 141 VICTORIA STREET
 KAMLOOPS, BC
 V2C 1Z5

25-Aug-04

No. of samples received: 15
 Sample type: Rock
 Project #: Gold Creek
 Shipment #: Not indicated
 Samples submitted by: Royanna Wild

ET #.	Tag #	Au (g/t)	Au (oz/t)	Ag (g/t)	Ag (oz/t)	Pb (%)	Zn (%)
9	GK-04-009	6.14	0.179	640	18.66	29.0	12.1

QC DATA:

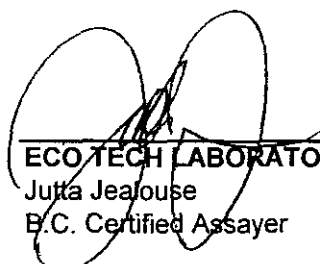
Repeat:

9	GK-04-009			640	18.66	29.4	12.5
---	-----------	--	--	-----	-------	------	------

Standard:

Pb106				58.8	1.72	0.52	0.84
OX123		1.83	0.053				

JJ/jm
 XLS/04


 ECO TECH LABORATORY LTD.
 Jutta Jealous
 B.C. Certified Assayer

ECO TECH LABORATORY LTD.
10041 Dallas Drive
KAMLOOPS, B.C.
V2C 6T4

ICP CERTIFICATE OF ANALYSIS AK 2004-992

NAVASOTA RESOURCES
#207 141 VICTORIA STREET
KAMLOOPS, BC
V2C 1Z5

Phone: 250-573-5700
Fax : 250-573-4557

No. of samples received: 15
Sample type: Rock
Project #: Gold Creek
Shipment #: Not indicated
Samples submitted by: Royanna Wild

Values in ppm unless otherwise reported

Et #.	Tag #	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
1	QV-04-001	<0.2	0.80	<5	10	5	0.14	<1	8 139	14	2.26	<10	0.53	398	15	<0.01	6	140	8	<5	<20	<1	0.04	<10	28	<10	3	28	
2	QV-04-002	<0.2	0.05	5	25	<5	0.04	<1	7 163	4	4.72	10	0.11	502	9	<0.01	17	300	<2	<5	<20	3	<0.01	<10	3	<10	2	58	
3	QV-04-003	<0.2	0.08	15	15	<5	0.02	<1	6 177	6	1.37	<10	0.03	305	18	<0.01	17	120	10	<5	<20	* 1	<0.01	<10	3	<10	1	32	
4	QV-04-004	<0.2	0.01	<5	5	<5	<0.01	<1	1 178	3	0.49	<10	<0.01	103	15	<0.01	7	50	<2	<5	<20	<1	<0.01	<10	1	<10	<1	9	
5	QV-04-005	3.5	0.11	65	65	<5	0.01	<1	3 198	12	1.49	<10	0.03	12	21	0.02	6	70	468	5	<20	5	<0.01	<10	4	<10	<1	78	
6	QV-04-008	<0.2	<0.01	<5	<5	<5	7.12	<1	<1 90	2	0.33	<10	0.07	310	9	<0.01	20	50	6	<5	<20	914	<0.01	<10	1	<10	6	4	
7	GK-04-006	<0.2	0.83	<5	225	<5	0.42	<1	6 99	39	1.83	20	0.73	172	9	<0.01	24	1840	16	<5	<20	3	0.02	<10	9	<10	11	59	
8	GK-04-007	<0.2	0.02	10	60	<5	>10	<1	2 10	5	0.55	<10	0.30	1155	<1	<0.01	94	330	24	<5	<20	1463	<0.01	<10	4	<10	9	18	
9	GK-04-009	>30	0.03	150	<5	75	0.06	831	27 77	966	8.15	20	0.10	<1	<1	<0.01	<1	150	>10000	445	<20	12	<0.01	<10	2	<10	<1	>10000	
10	GK-04-010	0.9	<0.01	5	<5	<5	<0.01	<1	<1 153	8	0.36	<10	<0.01	28	18	<0.01	4	20	338	<5	<20	<1	<0.01	<10	1	<10	<1	111	
11	GK-04-011	0.2	0.48	25	270	<5	0.12	<1	7 46	31	1.59	20	0.13	323	3	<0.01	29	420	32	<5	<20	14	<0.01	<10	7	<10	4	259	
12	GK-04-012	<0.2	<0.01	<5	<5	<5	<0.01	<1	<1 121	3	0.18	<10	<0.01	13	15	<0.01	3	<10	16	<5	<20	<1	<0.01	<10	<1	<10	<1	8	
13	GK-04-013	<0.2	<0.01	10	5	<5	<0.01	<1	<1 119	5	0.31	<10	<0.01	24	11	<0.01	5	20	16	<5	<20	<1	<0.01	<10	<1	<10	<1	25	
14	GK-04-014	<0.2	<0.01	<5	<5	<5	<0.01	<1	<1 152	4	0.27	<10	<0.01	32	18	<0.01	4	20	12	<5	<20	<1	<0.01	<10	<1	<10	<1	8	
15	GK-04-015	<0.2	<0.01	<5	<5	<5	<0.01	<1	<1 122	2	0.22	<10	<0.01	25	11	<0.01	3	<10	2	<5	<20	<1	<0.01	<10	<1	<10	<1	5	

QC DATA:**Repeat:**


1	QV-04-001	<0.2	0.79	<5	5	<5	0.13	<1	8 140	13	2.25	<10	0.53	395	15	<0.01	5	140	10	<5	<20	<1	0.04	<10	28	<10	3	36
---	-----------	------	------	----	---	----	------	----	-------	----	------	-----	------	-----	----	-------	---	-----	----	----	-----	----	------	-----	----	-----	---	----

Resplit:

1	QV-04-001	<0.2	0.80	<5	10	5	0.15	<1	9 172	15	2.28	<10	0.53	418	11	0.01	7	150	10	<5	<20	<1	0.05	<10	26	<10	3	31
---	-----------	------	------	----	----	---	------	----	-------	----	------	-----	------	-----	----	------	---	-----	----	----	-----	----	------	-----	----	-----	---	----

Standard:

GEO'04		1.4	1.49	55	135	<5	1.46	<1	18 55	83	3.32	10	0.89	573	<1	0.02	27	590	28	<5	<20	35	0.09	<10	42	<10	9	65
--------	--	-----	------	----	-----	----	------	----	-------	----	------	----	------	-----	----	------	----	-----	----	----	-----	----	------	-----	----	-----	---	----


ECO TECH LABORATORY LTD.
Jutta Jealous
BC Certified Assayer

ECO TECH LABORATORY LTD.
10041 Dallas Drive
KAMLOOPS, B.C.
V2C 6T4

ICP CERTIFICATE OF ANALYSIS AK 2004-1523

NAVASOTA RESOURCES
#207 141 VICTORIA STREET
KAMLOOPS, BC
V2C 1Z5

Phone: 250-573-5700
Fax : 250-573-4557

No. of samples received: 20

Sample type: Rock

Project #: Gold CK

Shipment #: None Given

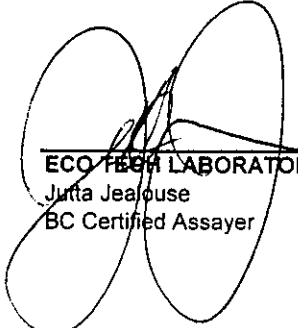
Samples submitted by: Royanna Wild

Values in ppm unless otherwise reported

Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
1	GK-04-020	<5	0.2	0.41	35	630	<5	0.06	<1	5	67	34	2.25	10	0.08	224	4	<0.01	39	390	6	<5	<20	17	<0.01	<10	7	<10	<1	98
2	GK-04-021	<5	<0.2	0.01	<5	10	<5	0.05	<1	<1	172	4	0.70	<10	<0.01	105	7	<0.01	6	300	<2	<5	<20	4	<0.01	<10	1	<10	<1	6
3	GK-04-022	425	0.2	0.01	10	15	<5	<0.01	<1	1	224	6	0.39	<10	<0.01	32	3	<0.01	7	30	2	<5	<20	<1	<0.01	<10	<1	<10	<1	1
4	GK-04-023	10	0.2	1.14	50	280	5	0.13	<1	42	100	61	7.67	<10	0.80	1482	6	0.05	54	350	8	<5	<20	9	<0.01	<10	107	<10	<1	89
5	GK-04-024	<5	0.2	0.12	<5	180	<5	<0.01	<1	<1	141	6	0.56	<10	<0.01	30	2	<0.01	5	90	4	<5	<20	2	<0.01	<10	3	<10	<1	23
6	GK-04-025	25	0.9	0.03	35	195	<5	<0.01	<1	<1	136	48	1.18	<10	<0.01	42	6	<0.01	6	90	324	<5	<20	2	<0.01	<10	2	<10	<1	78
7	GK-04-026	5	0.2	0.09	<5	145	<5	<0.01	<1	<1	75	3	0.17	<10	<0.01	16	<1	<0.01	2	30	4	<5	<20	<1	<0.01	<10	3	<10	<1	8
8	GK-04-027	15	0.2	0.10	10	110	<5	<0.01	<1	2	73	51	1.30	<10	<0.01	65	4	<0.01	9	270	8	<5	<20	3	<0.01	<10	3	<10	<1	65
9	GK-04-028	<5	0.2	0.06	30	630	<5	<0.01	<1	<1	194	12	0.90	<10	<0.01	68	3	<0.01	9	160	24	<5	<20	8	<0.01	<10	6	<10	<1	36
10	GK-04-029	5	1.9	0.19	<5	1030	<5	<0.01	<1	<1	92	27	1.27	<10	<0.01	30	10	<0.01	9	420	74	<5	<20	61	<0.01	<10	31	<10	<1	54
11	GK-04-030	<5	0.2	0.04	10	760	<5	<0.01	<1	<1	204	11	1.16	<10	<0.01	52	3	<0.01	8	180	10	<5	<20	2	<0.01	<10	4	<10	<1	28
12	GK-04-031	<5	<0.2	1.26	30	115	<5	0.05	<1	31	355	13	4.36	<10	0.95	826	9	0.01	109	220	10	<5	<20	<1	<0.01	<10	117	<10	<1	38
13	GK-04-032	<5	<0.2	0.07	<5	105	<5	0.01	<1	5	169	5	2.76	<10	0.01	423	4	<0.01	15	80	16	<5	<20	<1	<0.01	<10	4	<10	<1	177
14	GK-04-033	<5	<0.2	0.39	10	405	<5	1.55	<1	19	33	32	4.32	<10	0.40	756	3	0.05	11	380	8	<5	<20	82	<0.01	<10	13	<10	<1	74
15	GK-04-034	10	<0.2	0.06	45	185	<5	0.02	<1	3	129	6	1.46	<10	<0.01	137	6	<0.01	8	160	8	<5	<20	1	<0.01	<10	2	<10	<1	23
16	GK-04-035	<5	0.2	0.33	10	195	5	4.09	<1	21	18	20	5.11	<10	0.50	813	3	0.07	3	900	6	<5	<20	82	<0.01	<10	16	<10	<1	83
17	GK-04-036	<5	0.6	0.12	15	275	<5	0.04	<1	3	83	53	1.33	<10	0.02	145	4	<0.01	16	310	4	<5	<20	18	<0.01	<10	3	<10	<1	60
18	GK-04-037	<5	<0.2	0.15	10	1200	<5	0.03	<1	<1	93	40	1.19	<10	<0.01	147	2	<0.01	12	130	6	<5	<20	17	<0.01	<10	11	<10	<1	58
19	GK-04-038	5	<0.2	0.19	<5	370	<5	<0.01	<1	3	77	24	1.47	<10	0.02	64	4	0.01	21	250	6	<5	<20	3	<0.01	<10	6	<10	<1	81
20	GK-04-039	10	0.4	<0.01	10	10	<5	<0.01	<1	<1	203	4	0.37	<10	<0.01	24	3	<0.01	5	20	166	<5	<20	<1	<0.01	<10	<1	<10	<1	5

Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn	
QC DATA:																															
<i>Repeat:</i>																															
1	GK-04-020	<5	<0.2	0.42	35	665	<5	0.06	<1	5	68	32	2.23	10	0.08	220	4	0.01	39	390	8	<5	<20	19	<0.01	<10	8	<10	<1	98	
3	GK-04-022	430	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	
10	GK-04-029	5	2.0	0.21	<5	1110	<5	<0.01	<1	<1	94	27	1.28	<10	<0.01	28	10	<0.01	10	460	76	<5	<20	62	<0.01	<10	33	<10	<1	55	
<i>Standard:</i>																															
GEO'04		150	1.5	1.52	55	145	<5	1.40	<1	17	62	88	3.29	<10	0.81	597	<1	0.03	28	660	22	<5	<20	54	0.09	<10	57	<10	10	76	

JJ/sc
 #/1507
 XLS/04


 ECO TECH LABORATORY LTD.
 Jutta Jealous
 BC Certified Assayer

10-Nov-04

ECO TECH LABORATORY LTD.
10041 Dallas Drive
KAMLOOPS, B.C.
V2C 6T4

ICP CERTIFICATE OF ANALYSIS AK 2004-1720

NAVASOTA RESOURCES
#207 141 VICTORIA STREET
KAMLOOPS, BC
V2C 1Z5

Phone: 250-573-5700
Fax : 250-573-4557

No. of samples received: 12
Sample type: Rock
Project #: Gold Ck
Shipment #: None
Samples submitted by: Royanna Wild

Values in ppm unless otherwise reported

Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
1	GK-04-040	10	<0.2	0.98	115	120	5	0.51	<1	40	143	9	6.54	<10	0.65	1007	3	0.03	131	330	14	<5	<20	18	<0.01	<10	60	<10	1	54
2	GK-04-041	10	<0.2	0.69	20	55	<5	0.06	<1	15	127	10	2.91	<10	0.33	633	2	0.02	30	180	6	<5	<20	<1	<0.01	<10	36	<10	2	27
3	GK-04-042	135	1.4	0.17	75	190	<5	0.11	<1	1	48	22	2.35	<10	<0.01	46	8	<0.01	19	810	44	<5	<20	45	<0.01	<10	39	<10	<1	179
4	GK-04-043	10	0.2	0.70	25	1150	<5	0.38	<1	6	101	43	2.87	<10	0.52	945	2	0.02	38	490	16	<5	<20	73	<0.01	<10	27	<10	<1	100
5	GK-04-044	670	0.5	0.14	105	115	<5	0.25	<1	6	76	23	2.73	<10	0.05	64	3	<0.01	28	690	86	<5	<20	33	<0.01	<10	6	<10	<1	234
6	GK-04-045	20	0.2	<0.01	<5	5	<5	0.41	<1	1	158	4	0.55	<10	0.13	186	1	<0.01	9	80	<2	<5	<20	50	<0.01	<10	2	<10	<1	66
7	GK-04-046	5	0.2	1.57	<5	20	<5	0.64	<1	21	154	23	2.29	<10	1.70	244	<1	0.03	74	310	14	<5	<20	14	0.12	<10	18	<10	<1	26
8	GK-04-047	10	0.6	2.01	<5	35	<5	0.81	<1	29	47	36	3.01	<10	2.22	395	1	0.02	63	330	18	5	<20	19	0.17	<10	13	<10	<1	32
9	GK-04-048	10	<0.2	0.05	5	<5	<5	<0.01	<1	2	158	5	0.81	<10	<0.01	120	1	<0.01	9	<10	<2	<5	<20	<1	<0.01	<10	3	<10	<1	21
10	GK-04-049	20	0.2	0.79	230	200	5	2.58	<1	43	72	44	7.46	<10	1.75	1122	5	0.04	151	430	18	<5	<20	222	<0.01	<10	26	<10	<1	142
11	GK-04-050	45	0.4	0.55	30	300	<5	0.40	2	10	22	91	4.17	<10	0.17	971	2	0.02	14	830	36	<5	<20	34	<0.01	<10	9	<10	<1	301
12	GK-04-051	90	1.4	0.04	25	40	<5	<0.01	<1	<1	181	15	0.75	<10	<0.01	46	1	<0.01	7	80	470	<5	<20	<1	<0.01	<10	2	<10	<1	41

QC DATA:

Repeat:


1	GK-04-040	20	<0.2	0.95	110	120	5	0.49	<1	39	148	9	6.36	<10	0.63	980	4	0.03	127	310	10	<5	<20	19	<0.01	<10	58	<10	<1	51
---	-----------	----	------	------	-----	-----	---	------	----	----	-----	---	------	-----	------	-----	---	------	-----	-----	----	----	-----	----	-------	-----	----	-----	----	----

Resplit:

1	GK-04-040	25	<0.2	1.07	105	170	<5	0.56	<1	38	157	10	6.37	<10	0.69	982	3	0.05	127	280	12	<5	<20	24	<0.01	<10	65	<10	<1	53
---	-----------	----	------	------	-----	-----	----	------	----	----	-----	----	------	-----	------	-----	---	------	-----	-----	----	----	-----	----	-------	-----	----	-----	----	----

Standard:

GEO'04		140	1.5	1.57	60	140	<5	1.45	<1	18	61	89	4.03	<10	0.82	613	<1	0.03	28	700	20	<5	<20	51	0.09	<10	67	<10	9	74
--------	--	-----	-----	------	----	-----	----	------	----	----	----	----	------	-----	------	-----	----	------	----	-----	----	----	-----	----	------	-----	----	-----	---	----



ECO TECH LABORATORY LTD.
Jutta Jealous
BC Certified Assayer

ECO TECH LABORATORY LTD.
10041 Dallas Drive
KAMLOOPS, B.C.
V2C 6T4

ICP CERTIFICATE OF ANALYSIS AK 2004-993

NAVASOTA RESOURCES
#207 141 VICTORIA STREET
KAMLOOPS, BC
V2C 1Z5

Phone: 250-573-5700
Fax : 250-573-4557

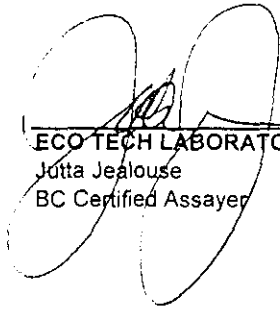
No. of samples received: 25
Sample type: Soil
Project #: Gold Creek
Shipment #: None Given
Samples submitted by: Royanna Wild

Values in ppm unless otherwise reported

Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
1	L103E 102+25N	75	4.3	3.12	65	660	<5	0.73	<1	32	76	163	5.42	20	0.76	1326	<1	0.02	143	920	66	<5	<20	38	0.10	<10	47	<10	41	151
2	L103E 102+50N	70	1.9	1.96	70	355	<5	0.72	<1	26	49	81	4.34	20	0.57	814	<1	0.01	105	810	42	<5	<20	42	0.02	<10	42	<10	14	107
3	L103E 102+75N	45	0.4	1.03	45	105	<5	0.21	<1	17	22	22	2.87	10	0.17	654	<1	0.01	23	1410	30	<5	<20	17	0.03	<10	29	<10	5	73
4	L103E 103+00N	25	0.4	1.64	50	120	<5	0.14	<1	14	29	17	3.29	10	0.19	572	<1	<0.01	22	780	32	<5	<20	7	0.08	<10	23	<10	3	86
5	L103E 103+25N	160	0.3	1.07	35	100	<5	0.08	<1	9	23	12	3.01	10	0.14	358	<1	<0.01	13	530	26	<5	<20	6	0.07	<10	27	<10	3	50
6	L103E 103+50N	55	0.3	0.74	50	125	<5	0.17	<1	11	22	15	3.35	10	0.14	511	<1	0.01	17	880	22	<5	<20	11	0.06	<10	25	<10	3	59
7	L103E 103+75N	255	0.4	0.70	70	100	<5	0.17	<1	10	21	18	2.91	10	0.15	357	<1	<0.01	21	700	32	<5	<20	10	0.06	<10	24	<10	3	66
8	L103E 104+00N	95	0.7	1.28	50	70	5	0.09	<1	10	20	13	3.10	<10	0.11	456	1	<0.01	13	960	26	<5	<20	7	0.08	<10	12	<10	3	42
9	L103E 104+25N	300	1.0	0.67	90	70	<5	0.05	<1	14	19	18	3.17	10	0.10	675	<1	<0.01	22	540	42	<5	<20	6	0.04	<10	29	<10	3	49
10	L103E 104+50N	45	2.6	1.94	95	100	<5	0.38	<1	30	26	29	3.62	20	0.22	813	<1	<0.01	60	830	40	<5	<20	33	0.04	<10	27	<10	10	95
11	L103E 104+75N	65	0.5	1.53	65	165	<5	0.18	<1	17	46	23	4.11	20	0.47	318	<1	<0.01	39	520	26	<5	<20	6	0.11	<10	39	<10	4	82
12	L103E 105+00N	35	0.4	1.43	25	180	<5	0.19	<1	18	45	25	3.95	20	0.49	656	<1	<0.01	29	520	20	<5	<20	6	0.14	<10	40	<10	5	64
13	L102E 102+75N	125	0.3	1.34	60	175	5	0.22	<1	17	41	42	4.14	10	0.33	353	2	<0.01	32	680	34	5	<20	13	0.12	<10	30	<10	6	74
14	L102E 103+00N	45	3.0	4.05	60	840	<5	0.52	<1	31	77	131	4.83	20	0.76	1774	<1	0.02	141	1000	72	<5	<20	35	0.12	<10	38	<10	30	141
15	L102E 103+25N	20	0.8	1.35	40	515	<5	0.47	<1	31	28	42	2.94	20	0.25	2724	<1	<0.01	32	880	34	<5	<20	31	0.05	<10	33	<10	10	89
16	L102E 103+50N	30	0.9	2.48	35	200	5	0.14	<1	22	51	51	4.15	10	0.47	1150	<1	<0.01	49	820	50	<5	<20	8	0.09	<10	47	<10	6	116
17	L102E 103+75N	35	0.2	1.20	60	210	<5	0.41	<1	29	39	54	4.47	20	0.46	1067	<1	<0.01	66	770	30	<5	<20	15	0.07	<10	27	<10	7	117
18	L102E 104+00N	5	0.7	1.69	25	170	<5	0.17	<1	14	35	32	3.53	10	0.24	546	<1	<0.01	28	780	30	<5	<20	10	0.11	<10	32	<10	4	75
19	L102E 104+25N	20	0.7	1.35	15	95	<5	0.08	<1	11	22	18	2.72	<10	0.15	730	<1	0.01	13	920	24	<5	<20	6	0.09	<10	23	<10	3	55
20	L102E 104+50N	20	0.3	0.72	20	65	<5	0.13	<1	9	23	14	2.90	<10	0.16	228	<1	<0.01	12	640	16	<5	<20	8	0.09	<10	28	<10	3	41
21	L102E 104+75N	25	1.0	0.93	15	95	5	0.08	<1	13	25	14	2.87	10	0.15	1277	<1	<0.01	13	600	20	<5	<20	6	0.10	<10	34	<10	4	44
22	L102E 105+00N	10	0.7	1.00	20	90	<5	0.09	<1	13	31	17	3.41	10	0.19	570	<1	<0.01	15	570	20	<5	<20	6	0.12	<10	36	<10	4	48
23	105+00N 102+25E	305	0.7	2.17	30	105	<5	0.14	<1	18	44	22	4.08	20	0.36	662	<1	<0.01	25	960	28	<5	<20	7	0.12	<10	38	<10	6	104
24	105+00N 102+50E	260	0.6	1.03	25	135	<5	0.16	<1	12	30	18	2.95	10	0.24	734	<1	<0.01	21	610	22	<5	<20	10	0.08	<10	35	<10	3	53
25	105+00N 102+75E	15	4.9	1.97	135	390	<5	0.58	<1	38	47	110	4.85	30	0.41	3391	<1	0.01	173	1290	64	<5	<20	53	0.04	<10	38	<10	47	122

Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn	
QC DATA:																															
<i>Repeat:</i>																															
1	L103E 102+25N	80	4.3	3.16	70	665	<5	0.73	<1	33	77	169	5.59	20	0.77	1337	<1	0.02	146	930	66	<5	<20	38	0.11	<10	41	<10	41	155	
7	L103E 103+75N	225	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	
8	L103E 104+00N	80	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-		
9	L103E 104+25N	305	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-		
10	L103E 104+50N	60	2.6	1.96	90	95	<5	0.38	<1	29	26	28	3.60	20	0.22	782	<1	0.01	60	860	40	<5	<20	33	0.04	<10	27	<10	10	96	
19	L102E 104+25N	25	0.7	1.30	15	95	<5	0.08	<1	11	23	18	2.73	<10	0.15	725	<1	0.01	12	900	24	<5	<20	6	0.08	<10	24	<10	4	55	
<i>Standard:</i>																															
	GEO'04	135	1.4	1.74	60	135	<5	1.63	<1	20	63	87	3.52	10	0.95	611	<1	0.03	31	640	26	<5	<20	46	0.12	<10	61	<10	9	66	

JJ/kk
df/5052
XLS/04


 ECO TECH LABORATORY LTD.
 Jutta Jealous
 BC Certified Assayer

ECO TECH LABORATORY LTD.
10041 Dallas Drive
KAMLOOPS, B.C.
V2C 6T4

ICP CERTIFICATE OF ANALYSIS AK 2004-1488

NAVASOTA RESOURCES
#207 141 VICTORIA STREET
KAMLOOPS, BC
V2C 1Z5

Phone: 250-573-5700
Fax : 250-573-4557

No. of samples received: 96
Sample type: Soil
Project #: Not Indicated
Shipment #: Not Indicated

Values in ppm unless otherwise reported

Et #.	Tag #	Au (ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
1	BL5000E 20000N	300	0.2	0.96	95	65	5	0.14	<1	17	25	42	4.18	<10	0.45	530	3	<0.01	58	520	20	<5	<20	6	0.07	<10	29	<10	<1	101
2	BL5000E 20025N	125	0.6	1.00	90	120	5	0.09	<1	15	18	26	3.60	<10	0.22	810	2	<0.01	37	940	22	<5	<20	6	0.06	<10	31	<10	<1	98
3	BL5000E 20050N	435	0.3	0.70	80	115	<5	0.09	<1	14	13	25	3.24	<10	0.19	576	3	<0.01	36	720	18	<5	<20	6	0.04	<10	25	<10	<1	95
4	BL5000E 20075N	65	1.1	1.25	45	115	<5	0.07	<1	13	13	21	2.47	<10	0.13	841	2	<0.01	21	690	12	<5	<20	5	0.04	<10	25	<10	<1	72
5	BL5000E 20100N	50	0.6	1.34	35	95	<5	0.10	<1	11	21	20	2.43	<10	0.26	975	2	<0.01	19	710	10	<5	<20	4	0.07	<10	26	<10	<1	59
6	BL5000E 20125N	90	0.3	1.09	95	65	5	0.14	<1	16	31	36	4.05	<10	0.50	301	2	<0.01	51	630	12	<5	<20	4	0.09	<10	35	<10	<1	78
7	BL5000E 20150N	25	0.4	1.14	20	160	<5	0.12	<1	13	29	18	2.88	<10	0.38	1279	2	<0.01	28	540	10	<5	<20	4	0.08	<10	47	<10	<1	67
8	BL5000E 20175N	100	0.5	0.86	80	85	5	0.05	<1	21	13	50	3.91	<10	0.20	727	3	<0.01	60	550	16	<5	<20	5	0.02	<10	21	<10	<1	113
9	BL5000E 20200N	225	0.4	1.20	35	95	<5	0.09	<1	13	22	23	3.10	<10	0.25	783	2	<0.01	26	570	12	<5	<20	3	0.07	<10	40	<10	<1	62
10	BL5000E 20225N	15	0.8	1.12	10	75	<5	0.16	<1	9	15	19	2.19	<10	0.11	791	2	<0.01	9	530	10	<5	<20	10	0.05	<10	28	<10	<1	38
11	BL5000E 20250N	35	0.5	0.98	35	65	<5	0.07	<1	12	16	21	2.64	<10	0.14	732	2	<0.01	22	530	16	<5	<20	4	0.05	<10	32	<10	<1	55
12	BL5000E 20275N	50	0.5	1.13	100	110	<5	0.11	<1	24	26	53	4.01	<10	0.37	695	3	<0.01	71	500	24	<5	<20	7	0.06	<10	28	<10	<1	102
13	BL5000E 20300N	85	0.9	0.79	75	105	5	0.12	<1	15	14	32	2.94	<10	0.18	508	2	<0.01	46	460	20	<5	<20	11	0.03	<10	27	<10	<1	70
14	BL5000E 20325N	30	0.3	1.16	35	115	<5	0.12	<1	17	32	38	3.20	<10	0.53	460	3	<0.01	53	420	10	<5	<20	6	0.07	<10	32	<10	<1	82
15	BL5000E 20350N	30	0.4	1.40	50	100	5	0.15	<1	17	33	44	3.20	<10	0.55	328	2	<0.01	50	360	8	<5	<20	6	0.08	<10	33	<10	<1	73
16	BL5000E 20375N	355	0.4	1.09	140	240	<5	0.13	<1	24	23	46	4.68	<10	0.28	655	4	<0.01	59	440	20	<5	<20	16	0.07	<10	33	<10	<1	97
17	BL5000E 20400N	25	0.2	0.61	115	150	<5	0.05	<1	31	15	46	4.13	<10	0.11	1543	3	<0.01	73	450	20	<5	<20	5	0.01	<10	25	<10	<1	94
18	BL5000E 20425N	20	0.4	1.28	20	135	5	0.17	<1	14	32	24	2.72	<10	0.40	718	1	<0.01	25	360	10	<5	<20	10	0.09	<10	40	<10	4	65
19	BL5000E 20450N	30	1.1	1.61	30	295	<5	0.31	<1	18	38	71	2.98	<10	0.48	1255	2	<0.01	69	510	14	<5	<20	28	0.08	<10	40	<10	73	91
20	BL5000E 20475N	175	0.4	1.46	20	120	5	0.19	<1	14	37	29	3.04	<10	0.59	431	2	<0.01	29	440	8	<5	<20	6	0.11	<10	38	<10	<1	70
21	BL5000E 20500N	60	0.8	0.87	30	120	<5	0.15	<1	14	24	27	2.75	<10	0.24	1006	3	<0.01	20	530	16	<5	<20	9	0.06	<10	44	<10	<1	72
22	BL5000E 20525N	30	0.3	0.59	210	100	5	0.14	<1	35	19	60	4.65	<10	0.33	621	3	<0.01	129	430	18	<5	<20	12	0.03	<10	18	<10	<1	142
23	BL5000E 20550N	50	<0.2	1.68	40	85	10	0.25	<1	18	44	40	3.10	<10	0.77	424	2	<0.01	43	370	8	<5	<20	5	0.13	<10	31	<10	11	77
24	BL5000E 20575N	80	<0.2	1.70	20	100	<5	0.26	<1	20	52	50	3.13	<10	0.94	504	2	<0.01	41	290	6	<5	<20	7	0.14	<10	33	<10	12	61
25	BL5000E 20600N	80	0.2	1.47	30	110	5	0.22	<1	19	43	40	3.26	<10	0.70	674	2	<0.01	39	550	12	<5	<20	8	0.10	<10	38	<10	4	80

Et #.	Tag #	Au (ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
26	BL5000E 20625N	260	0.6	1.62	45	85	<5	0.24	<1	17	50	46	3.52	<10	0.81	400	2	<0.01	41	410	218	<5	<20	8	0.11	<10	39	<10	4	157
27	BL5000E 20650N	50	<0.2	1.59	25	105	5	0.26	<1	18	44	34	3.22	<10	0.80	433	2	<0.01	45	330	12	<5	<20	7	0.13	<10	31	<10	8	79
28	BL5000E 20675N	40	1.1	2.16	60	155	5	0.12	<1	27	45	52	4.22	<10	0.55	477	3	<0.01	59	620	16	<5	<20	7	0.07	<10	47	<10	22	121
29	BL5000E 20700N	30	0.2	1.48	40	80	<5	0.20	<1	20	39	44	3.29	<10	0.73	456	2	<0.01	53	240	16	<5	<20	7	0.11	<10	26	<10	4	80
30	BL5000E 20725N	40	0.2	0.44	80	70	<5	0.08	<1	32	9	70	4.96	<10	0.17	658	4	<0.01	92	420	22	<5	<20	12	<0.01	<10	13	<10	<1	157
31	BL5000E 20750N	25	<0.2	1.68	30	80	5	0.19	<1	15	40	28	3.04	<10	0.70	316	1	<0.01	35	290	8	<5	<20	5	0.11	<10	28	<10	4	62
32	BL5000E 20775N	20	<0.2	1.74	25	95	5	0.19	<1	15	41	29	3.12	<10	0.70	295	2	<0.01	34	380	8	<5	<20	7	0.11	<10	35	<10	2	62
33	BL5000E 20800N	45	0.2	1.66	15	75	10	0.19	<1	13	40	18	2.73	<10	0.65	326	2	<0.01	23	310	24	<5	<20	4	0.15	<10	37	<10	6	67
34	BL5000E 20825N	5	<0.2	1.28	<5	60	<5	0.27	<1	14	38	22	2.24	<10	0.76	370	<1	<0.01	27	300	4	<5	<20	5	0.16	<10	22	<10	10	46
35	BL5000E 20850N	25	0.2	1.51	20	95	10	0.18	<1	15	38	25	3.04	<10	0.70	379	1	<0.01	37	260	6	<5	<20	6	0.12	<10	31	<10	3	65
36	BL5000E 20875N	20	0.2	1.57	20	115	<5	0.29	<1	20	49	38	3.35	<10	0.79	496	1	<0.01	48	530	16	<5	<20	10	0.11	<10	34	<10	8	66
37	BL5000E 20900N	30	0.2	1.44	20	75	10	0.32	<1	21	51	32	3.09	<10	0.79	463	2	<0.01	40	510	20	<5	<20	7	0.12	<10	34	<10	12	76
38	BL5000E 20925N	90	0.2	1.24	105	110	<5	0.21	<1	28	38	65	4.81	<10	0.58	626	4	<0.01	69	530	30	<5	<20	11	0.05	<10	35	<10	<1	111
39	BL5000E 20950N	50	0.4	1.23	40	170	<5	0.32	<1	22	35	41	3.47	<10	0.45	1241	3	<0.01	44	690	44	<5	<20	13	0.06	<10	39	<10	5	109
40	BL5000E 20975N	60	0.5	1.35	45	95	5	0.08	<1	19	25	32	4.27	<10	0.23	911	4	<0.01	35	830	32	<5	<20	4	0.04	<10	32	<10	<1	92
41	BL5000E 21000N	105	0.5	0.92	165	115	5	0.12	<1	37	20	74	7.82	<10	0.20	1154	6	<0.01	83	1860	48	<5	<20	8	0.02	<10	29	<10	<1	117
42	BL5000E 21025N	295	1.2	1.37	135	90	5	0.08	<1	16	25	26	5.78	<10	0.18	525	5	<0.01	34	1260	40	<5	<20	4	0.05	<10	37	<10	<1	113
43	BL5000E 21050N	5	1.1	1.49	10	135	<5	0.13	<1	13	32	20	3.06	<10	0.27	796	2	<0.01	18	520	24	<5	<20	5	0.11	<10	41	<10	<1	100
44	BL5000E 21075N	30	0.8	1.36	10	195	<5	0.46	<1	12	35	42	2.78	<10	0.35	686	2	<0.01	32	440	44	<5	<20	25	0.10	<10	41	<10	38	102
45	BL5000E 21100N	15	0.2	1.27	10	145	<5	0.29	<1	17	46	40	2.96	<10	0.80	561	2	<0.01	42	430	16	<5	<20	9	0.08	<10	34	<10	11	72
46	BL5000E 21125N	10	1.1	2.24	10	330	<5	0.71	1	17	45	96	3.04	<10	0.48	1752	2	<0.01	68	820	32	<5	<20	44	0.05	<10	40	<10	77	115
47	BL5000E 21150N	15	0.4	1.17	20	125	<5	0.27	<1	14	41	52	2.56	<10	0.60	293	3	<0.01	41	510	24	<5	<20	14	0.07	<10	36	<10	15	87
48	BL5000E 21175N	<5	0.2	2.47	10	75	5	0.16	<1	10	40	27	2.28	<10	0.36	162	1	<0.01	20	280	20	<5	<20	6	0.12	<10	18	<10	40	30
49	BL5000E 21200N	<5	0.3	1.51	5	60	10	0.21	<1	16	51	19	2.81	<10	0.66	309	<1	<0.01	23	240	14	<5	<20	4	0.20	<10	24	<10	12	51
50	BL5000E 21225N	5	0.2	1.53	5	85	10	0.24	<1	16	48	22	2.59	<10	0.66	371	<1	<0.01	25	260	14	<5	<20	3	0.16	<10	26	<10	14	50
51	BL5000E 21250N	<5	<0.2	1.53	<5	65	10	0.29	<1	17	51	18	2.76	<10	0.79	394	<1	<0.01	28	390	12	<5	<20	6	0.16	<10	27	<10	12	53
52	BL5000E 21275N	<5	<0.2	1.64	<5	75	10	0.26	<1	16	51	18	2.77	<10	0.78	309	1	<0.01	26	260	14	<5	<20	3	0.15	<10	27	<10	10	57
53	BL5000E 21300N	<5	<0.2	1.29	<5	120	10	0.24	<1	13	40	15	3.13	<10	0.48	273	1	<0.01	17	220	14	<5	<20	11	0.15	<10	41	<10	7	49
54	BL5000E 21325N	5	1.1	1.84	10	210	<5	0.40	<1	20	63	85	3.15	<10	0.80	1045	1	<0.01	44	410	18	<5	<20	18	0.11	<10	34	<10	120	70
55	BL5000E 21350N	<5	1.1	1.60	10	105	<5	0.31	<1	20	52	39	3.20	<10	0.96	646	1	<0.01	40	440	14	<5	<20	8	0.09	<10	33	<10	19	68
56	BL5000E 21375N	<5	<0.2	1.70	5	85	<5	0.31	<1	19	51	43	3.25	<10	0.92	441	<1	<0.01	35	390	16	<5	<20	6	0.13	<10	31	<10	14	63
57	BL5000E 21400N	<5	<0.2	1.38	<5	120	<5	0.30	<1	16	53	45	2.68	<10	0.99	419	1	<0.01	37	400	10	<5	<20	5	0.12	<10	33	<10	14	54
58	BL5000E 21425N	<5	<0.2	1.85	10	85	5	0.32	<1	23	60	42	2.96	<10	0.96	435	<1	<0.01	40	500	18	<5	<20	4	0.12	<10	31	<10	14	64
59	BL5000E 21450N	<5	<0.2	0.80	<5	165	10	0.32	<1	10	34	16	2.63	<10	0.33	540	1	<0.01	15	490	12	<5	<20	13	0.11	<10	42	<10	<1	50
60	BL5000E 21475N	45	0.3	0.75	5	145	5	0.12	<1	19	27	21	2.98	<10	0.22	1387	2	<0.01	18	390	16	<5	<20	8	0.08	<10	42	<10	<1	54
61	BL5000E 21500N	15	0.2	1.96	5	90	10	0.20	<1	25	53	29	3.73	<10	0.70	292	3	<0.01	38	460	20	<5	<20	5	0.11	<10	38	<10	4	97
62	BL5000E 21525N	10	0.2	0.24	5	70	<5	0.04	<1	8	6	16	2.38	<10	0.03	109	3	<0.01	17	330	8	<5	<20	5	0.01	<10	29	<10	<1	49
63	BL5000E 21550N	<5	0.5	0.45	<5	100	<5	0.08	<1	4	16	11	1.55	<10	0.09	125	2	<0.01	7	400	12	<5	<20	7	0.07	<10	35	<10	<1	24
64	BL5000E 21575N	5	0.3	1.03	<5	85	10	0.12	<1	10	34	17	2.92	<10	0.33	316	2	<0.01	14	350	18	<5	<20	3	0.13	<10	38	<10	4	40
65	BL5000E 21600N	<5	0.2	1.26	<5	80	5	0.12	<1	9	35	14	2.70	<10	0.32	188	1	<0.01	14	400	14	<5	<20	4	0.13	<10	35	<10	2	43

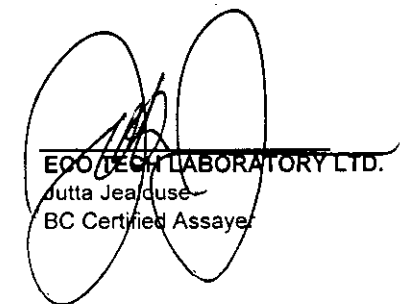
Et #.	Tag #	Au (ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
66	BL5000E 21625N	5	0.2	1.39	<5	75	10	0.13	<1	13	46	20	3.47	<10	0.46	257	1	<0.01	19	310	16	<5	<20	2	0.19	<10	54	<10	6	39
67	BL5000E 21650N	5	0.3	2.76	15	245	<5	0.31	<1	14	44	72	2.10	20	0.28	873	2	0.02	25	710	26	<5	<20	26	0.08	<10	30	<10	132	42
68	BL5000E 21675N	5	0.3	1.31	<5	140	5	0.15	<1	15	50	24	3.07	<10	0.53	664	2	<0.01	23	300	16	<5	<20	4	0.15	<10	50	<10	7	56
69	BL5000E 21700N	<5	0.3	1.05	<5	130	5	0.15	<1	7	24	13	2.45	<10	0.17	288	2	<0.01	10	530	16	<5	<20	8	0.08	<10	30	<10	<1	37
70	BL5000E 21725N	5	<0.2	0.45	<5	85	<5	0.07	<1	4	15	10	1.53	<10	0.08	115	1	<0.01	7	390	10	<5	<20	7	0.06	<10	33	<10	<1	23
71	BL5000E 21750N	<5	0.5	1.93	5	135	10	0.16	<1	11	50	15	2.80	<10	0.44	301	3	<0.01	21	450	16	<5	<20	6	0.11	<10	40	<10	5	56
72	BL5000E 21775N	5	0.3	1.57	<5	90	<5	0.21	<1	11	48	17	3.03	<10	0.53	223	2	<0.01	23	440	16	<5	<20	5	0.14	<10	40	<10	3	62
73	BL5000E 21800N	5	0.3	1.15	<5	85	10	0.14	<1	8	32	11	2.39	<10	0.27	202	2	<0.01	14	350	14	<5	<20	4	0.13	<10	38	<10	2	40
74	BL5000E 21825N	<5	0.3	0.98	<5	105	10	0.18	<1	11	33	11	2.73	<10	0.31	511	2	<0.01	16	400	14	<5	<20	5	0.10	<10	38	<10	<1	63
75	BL5000E 21850N	10	0.2	1.30	<5	110	5	0.29	<1	14	44	14	3.01	<10	0.46	560	2	<0.01	20	370	22	<5	<20	10	0.12	<10	38	<10	6	80
76	BL5000E 21875N	5	<0.2	1.78	<5	120	10	0.35	<1	17	69	21	3.50	<10	0.83	463	1	<0.01	38	390	18	<5	<20	7	0.18	<10	47	<10	9	83
77	BL5000E 21900N	15	0.2	0.85	<5	160	<5	0.42	<1	6	21	9	2.16	<10	0.21	775	2	<0.01	9	510	14	<5	<20	22	0.05	<10	24	<10	1	82
78	BL5000E 21925N	5	<0.2	1.73	<5	140	10	0.25	<1	14	49	17	3.19	<10	0.55	466	2	<0.01	27	320	24	<5	<20	12	0.11	<10	46	<10	6	99
79	BL5000E 21950N	5	<0.2	2.11	10	140	5	0.19	<1	14	59	32	3.28	<10	0.77	324	2	<0.01	37	460	18	<5	<20	7	0.08	<10	43	<10	2	85
80	BL5000E 21975N	5	0.6	1.88	5	130	<5	0.30	<1	19	46	29	2.62	<10	0.55	902	2	<0.01	38	480	20	<5	<20	23	0.06	<10	44	<10	21	139
81	BL5000E 22000N	5	0.3	1.68	5	195	<5	0.40	<1	13	40	22	2.78	<10	0.36	390	2	<0.01	26	390	20	<5	<20	26	0.08	<10	36	<10	15	158
82	BL5000E 22025N	5	0.3	1.10	<5	60	5	0.12	<1	10	34	16	2.73	<10	0.29	254	2	<0.01	21	410	18	<5	<20	4	0.09	<10	33	<10	1	77
83	BL5000E 22050N	5	0.2	1.00	<5	55	5	0.13	<1	9	30	13	2.66	<10	0.26	193	2	<0.01	14	370	16	<5	<20	5	0.10	<10	18	<10	3	44
84	BL5000E 22075N	10	0.6	1.30	<5	65	10	0.12	<1	10	38	20	2.93	<10	0.26	242	3	<0.01	18	380	20	<5	<20	5	0.11	<10	37	<10	3	52
85	BL5000E 22100N	5	0.3	2.33	10	100	5	0.14	1	17	44	34	3.26	<10	0.40	570	4	<0.01	28	610	22	<5	<20	5	0.08	<10	23	<10	16	149
86	BL5000E 22125N	5	0.2	1.08	<5	85	10	0.18	<1	10	37	13	2.76	<10	0.32	722	2	<0.01	18	580	14	<5	<20	5	0.11	<10	41	<10	3	50
87	BL5000E 22150N	10	0.4	1.95	5	135	5	0.31	<1	20	47	30	2.69	<10	0.57	945	2	0.01	37	510	22	<5	<20	24	0.06	<10	42	<10	23	143
88	BL5000E 22175N	<5	0.7	1.27	10	180	5	0.16	<1	13	40	22	2.90	<10	0.33	3128	3	<0.01	27	490	22	<5	<20	8	0.07	<10	49	<10	2	117
89	BL5000E 22200N	<5	1.6	1.50	<5	60	10	0.11	<1	8	35	17	2.89	<10	0.29	209	2	<0.01	15	380	16	<5	<20	4	0.11	<10	38	<10	3	48
90	BL5000E 22225N	5	1.2	2.10	<5	60	10	0.20	<1	15	53	20	3.37	<10	0.56	356	2	<0.01	23	470	18	<5	<20	5	0.15	<10	27	<10	9	69
91	BL5000E 22250N	25	0.5	2.39	<5	120	10	0.26	<1	30	81	36	3.72	<10	1.02	734	2	<0.01	45	280	22	<5	<20	6	0.22	<10	43	<10	16	97
92	BL5000E 22275N	<5	0.6	2.02	<5	105	10	0.22	<1	21	63	29	3.41	<10	0.73	523	3	<0.01	28	250	18	<5	<20	5	0.17	<10	40	<10	27	62
93	BL5000E 22300N	<5	1.5	2.10	<5	100	<5	0.11	<1	15	44	44	2.60	<10	0.39	303	3	<0.01	23	370	22	<5	<20	4	0.09	<10	43	<10	26	47
94	BL5000E 22325N	<5	1.1	1.32	<5	60	5	0.13	<1	7	28	16	1.90	<10	0.21	152	2	<0.01	11	380	14	<5	<20	4	0.11	<10	27	<10	11	27
95	BL5000E 22350N	<5	0.9	1.72	<5	65	5	0.16	<1	10	40	17	2.83	<10	0.36	162	3	<0.01	16	320	22	<5	<20	3	0.12	<10	35	<10	15	37
96	BL5000E 22375N	5	1.7	3.78	15	45	<5	0.07	<1	4	18	13	0.88	<10	0.11	42	2	<0.01	8	1160	28	<5	<20	3	0.06	<10	9	<10	14	20

IC DATA:

Repeat:

1	BL5000E 20000N	250	0.3	1.02	85	65	<5	0.14	<1	17	25	37	4.18	<10	0.43	560	2	<0.01	56	550	20	<5	<20	6	0.07	<10	28	<10	<1	90
3	BL5000E 20050N	500	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-
4	BL5000E 20075N	50	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-
5	BL5000E 20100N	35	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-
6	BL5000E 20125N	65	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-
8	BL5000E 20175N	105	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-
9	BL5000E 20200N	205	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-
10	BL5000E 20225N	15	0.7	1.09	10	75	5	0.15	<1	9	15	19	2.16	<10	0.10	798	2	<0.01	9	530	10	<5	<20	10	0.06	<10	28	<10	<1	38
13	BL5000E 20300N	95	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-

Et #.	Tag #	Au (ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Tl %	U	V	W	Y	Zn
16	BL5000E 20375N	315	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-
19	BL5000E 20450N	60	1.0	1.54	35	285	<5	0.30	<1	17	36	67	2.94	<10	0.47	1216	1	<0.01	68	480	16	<5	<20	27	0.07	<10	37	<10	69	91
25	BL5000E 20600N	75	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-
26	BL5000E 20625N	315	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-
28	BL5000E 20675N	45	1.1	2.22	65	150	5	0.13	<1	30	47	53	4.47	<10	0.58	490	4	<0.01	61	600	16	<5	<20	9	0.08	<10	48	<10	21	126
36	BL5000E 20875N	20	0.2	1.61	20	125	5	0.29	<1	20	52	39	3.45	<10	0.80	490	2	<0.01	50	530	18	<5	<20	8	0.11	<10	39	<10	7	71
45	BL5000E 21100N	<5	0.2	1.24	10	140	<5	0.30	<1	17	46	39	2.94	<10	0.78	542	1	<0.01	41	430	16	<5	<20	9	0.07	<10	30	<10	11	73
54	BL5000E 21325N	5	1.2	1.78	10	210	<5	0.39	<1	19	66	80	3.10	<10	0.81	995	1	<0.01	42	380	18	<5	<20	18	0.12	<10	37	<10	119	68
71	BL5000E 21750N	5	0.5	1.94	10	130	5	0.17	<1	11	51	15	2.85	<10	0.46	299	2	<0.01	21	510	16	<5	<20	4	0.12	<10	39	<10	6	56
89	BL5000E 22200N	<5	1.4	1.55	<5	65	5	0.11	<1	9	37	18	2.96	<10	0.29	213	2	<0.01	15	400	18	<5	<20	4	0.11	<10	35	<10	3	48
Standard:																														
	GEO'04	140	1.5	1.50	50	145	<5	1.14	<1	18	60	85	2.74	<10	0.82	521	1	0.02	29	490	22	<5	<20	54	0.12	<10	60	<10	11	74
	GEO'04	140	1.5	1.52	50	145	<5	1.32	<1	20	58	86	3.14	<10	0.83	578	<1	0.02	28	690	22	<5	<20	52	0.09	<10	60	<10	11	75
	GEO'04	140	1.4	1.51	55	145	<5	1.30	<1	20	59	84	3.06	<10	0.81	564	<1	0.02	29	630	22	<5	<20	53	0.09	<10	60	<10	10	76


 ECO TECH LABORATORY LTD.
 Jutta Jeanduse
 BC Certified Assayer

ECO TECH LABORATORY LTD.
10041 Dallas Drive
KAMLOOPS, B.C.
V2C 6T4

ICP CERTIFICATE OF ANALYSIS AK 2004-1491

NAVASOTA RESOURCES
#207 141 VICTORIA STREET
KAMLOOPS, BC
V2C 1Z5

Phone: 250-573-5700
Fax : 250-573-4557

No. of samples received: 80
Sample type: Soil
Project #: Not Indicated
Shipment #: Not Indicated

Values in ppm unless otherwise reported

Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
1	L20000N 4500E	5	0.3	1.51	10	165	5	0.60	<1	11	36	45	2.60	<10	0.50	288	2	0.01	21	320	24	<5	<20	21	0.14	<10	33	<10	34	89
2	L20000N 4525E	5	0.6	1.81	30	145	<5	1.02	<1	8	58	133	1.81	<10	0.24	596	1	0.02	17	680	14	<5	<20	24	0.06	<10	37	<10	71	47
3	L20000N 4550E	25	0.3	1.48	15	175	<5	0.80	<1	12	42	52	2.20	<10	0.38	472	1	0.02	20	490	10	<5	<20	20	0.08	<10	33	<10	40	56
4	L20000N 4575E	5	0.4	1.77	10	210	<5	0.81	<1	16	41	56	2.59	<10	0.60	581	1	0.01	24	490	10	<5	<20	24	0.13	<10	32	<10	31	67
5	L20000N 4600E	5	<0.2	1.40	<5	160	10	0.35	<1	16	50	32	3.22	<10	0.67	298	<1	0.01	27	280	10	<5	<20	15	0.24	<10	37	<10	20	45
6	L20000N 4625E	10	<0.2	1.30	<5	165	10	0.21	<1	16	44	18	3.03	<10	0.54	969	<1	0.01	22	410	10	<5	<20	7	0.22	<10	44	<10	12	61
7	L20000N 4650E	5	0.2	1.47	<5	130	10	0.20	<1	13	48	25	3.08	<10	0.54	272	1	0.01	21	320	10	<5	<20	8	0.23	<10	42	<10	18	61
8	L20000N 4675E	5	<0.2	1.62	<5	110	10	0.24	<1	16	52	23	3.19	<10	0.73	384	<1	0.01	25	350	10	<5	<20	6	0.24	<10	41	<10	14	52
9	L20000N 4700E	15	0.2	1.75	5	230	10	0.40	<1	20	57	50	3.13	<10	0.83	555	<1	0.01	39	470	10	<5	<20	20	0.20	<10	40	<10	33	62
10	L20000N 4725E	10	0.9	2.11	10	490	<5	0.47	<1	25	49	81	2.78	<10	0.65	891	1	0.01	51	760	14	<5	<20	55	0.10	<10	51	<10	63	90
11	L20000N 4750E	5	<0.2	1.73	<5	205	10	0.28	<1	19	54	25	3.45	<10	0.78	417	1	0.01	31	320	10	<5	<20	7	0.26	<10	42	<10	17	61
12	L20000N 4775E	10	<0.2	1.72	5	150	5	0.32	<1	16	49	35	3.08	<10	0.85	290	1	0.01	31	480	10	<5	<20	8	0.22	<10	35	<10	19	57
13	L20000N 4800E	5	0.3	0.77	10	305	5	0.32	<1	12	18	18	2.49	<10	0.16	1527	1	0.02	15	570	16	<5	<20	24	0.10	<10	34	<10	5	83
14	L20000N 4825E	10	<0.2	1.15	<5	245	5	0.34	<1	17	36	15	2.87	<10	0.38	1342	1	0.01	19	620	10	<5	<20	13	0.14	<10	42	<10	8	104
15	L20000N 4850E	40	0.2	1.39	30	245	5	0.34	<1	17	41	39	3.44	<10	0.60	720	2	0.01	44	630	14	<5	<20	13	0.14	<10	41	<10	9	93
16	L20000N 4875E	345	<0.2	1.30	105	115	10	0.25	<1	23	43	53	4.67	<10	0.65	453	2	<0.01	72	420	20	<5	<20	6	0.14	<10	29	<10	2	110
17	L20000N 4900E	280	0.5	0.86	50	285	<5	0.37	<1	15	18	33	3.10	<10	0.15	819	2	0.03	32	860	20	<5	<20	33	0.06	<10	34	<10	4	64
18	L20000N 4925E	80	2.5	2.25	65	560	<5	0.68	<1	25	60	142	4.19	10	0.62	1100	2	0.02	142	830	42	<5	<20	50	0.06	<10	44	<10	110	124
19	L20000N 4950E	155	1.1	1.07	75	220	5	0.47	<1	18	18	29	3.36	<10	0.19	1137	2	0.01	50	810	26	<5	<20	38	0.05	<10	27	<10	10	127
20	L20000N 4975E	80	0.4	0.55	60	135	5	0.18	<1	9	13	18	3.12	<10	0.07	549	2	<0.01	29	640	20	<5	<20	9	0.07	<10	29	<10	<1	80
21	L20000N 5025E	45	0.7	1.08	90	160	5	0.16	<1	20	32	34	4.03	<10	0.36	919	3	<0.01	53	570	20	<5	<20	6	0.07	<10	41	<10	<1	101
22	L20000N 5050E	250	0.8	0.90	270	145	<5	0.26	<1	27	11	69	4.84	<10	0.10	925	3	0.01	85	780	28	<5	<20	23	0.01	<10	23	<10	2	80
23	L20000N 5075E	75	0.4	0.65	75	120	5	0.18	<1	12	14	22	3.71	<10	0.10	296	3	0.01	32	550	24	<5	<20	13	0.06	<10	34	<10	<1	83
24	L20000N 5100E	160	0.4	0.58	95	75	5	0.08	<1	12	15	36	4.33	<10	0.16	321	3	<0.01	48	800	40	<5	<20	3	0.04	<10	29	<10	<1	118
25	L20000N 5125E	340	0.8	1.08	155	105	15	0.11	<1	24	28	42	6.03	<10	0.29	395	4	<0.01	62	900	28	<5	<20	3	0.08	<10	37	<10	<1	113

Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
26	L20000N 5150E	25	0.7	1.17	70	135	5	0.33	<1	12	21	22	4.09	<10	0.13	709	3	0.01	28	620	26	<5	<20	19	0.09	<10	30	<10	<1	112
27	L20000N 5175E	30	1.3	1.27	35	55	5	0.04	<1	7	10	18	2.88	<10	0.02	176	3	0.01	18	870	26	<5	<20	2	0.05	<10	21	<10	<1	48
28	L20000N 5200E	65	1.5	0.63	70	60	<5	0.05	<1	9	10	18	3.30	<10	0.08	185	3	<0.01	30	640	20	<5	<20	3	0.05	<10	25	<10	<1	58
29	L20000N 5225E	20	0.4	0.36	30	45	5	0.04	<1	7	9	12	2.08	<10	0.03	84	1	0.01	17	290	10	<5	<20	2	0.09	<10	25	<10	<1	36
30	L20000N 5250E	20	0.6	0.50	35	50	<5	0.06	<1	8	9	19	2.93	<10	0.03	233	2	0.02	27	380	12	<5	<20	3	0.05	<10	25	<10	<1	44
31	L20000N 5275E	15	0.4	0.26	25	40	5	0.07	<1	6	6	14	2.03	<10	0.02	138	2	<0.01	21	380	10	<5	<20	4	0.02	<10	26	<10	<1	43
32	L20000N 5300E	20	0.9	0.76	35	95	5	0.07	<1	18	21	23	3.59	<10	0.15	1521	2	0.01	33	720	16	<5	<20	2	0.06	<10	31	<10	<1	76
33	L20000N 5325E	75	0.9	0.85	75	135	<5	0.37	<1	17	11	40	3.47	<10	0.09	667	2	0.01	68	570	20	<5	<20	35	0.04	<10	24	<10	12	80
34	L20000N 5350E	25	2.0	2.23	30	160	<5	0.14	<1	19	18	75	2.66	<10	0.11	2009	1	0.02	123	770	34	<5	<20	12	0.06	<10	18	<10	48	101
35	L20000N 5375E	10	0.4	0.63	20	90	5	0.08	<1	14	15	18	3.18	<10	0.09	880	2	<0.01	24	720	16	<5	<20	4	0.05	<10	29	<10	<1	60
36	L20000N 5400E	10	0.2	0.82	15	100	5	0.11	<1	16	19	17	3.37	<10	0.12	1274	2	0.01	25	700	14	<5	<20	6	0.07	<10	26	<10	<1	71
37	L20000N 5425E	5	0.2	0.79	15	130	5	0.14	<1	14	22	17	3.36	<10	0.16	887	2	<0.01	26	1000	16	<5	<20	5	0.05	<10	34	<10	<1	78
38	L20000N 5450E	20	2.5	2.52	45	440	<5	0.68	<1	36	76	112	5.10	10	0.80	1939	3	0.02	167	1000	38	<5	<20	58	0.07	<10	44	<10	119	151
39	L20000N 5475E	25	2.7	2.85	40	505	<5	0.58	<1	32	86	139	5.32	<10	0.64	2668	2	0.02	201	1060	38	<5	<20	55	0.08	<10	41	<10	68	188
40	L20000N 5500E	5	1.5	1.75	20	185	<5	0.33	<1	19	33	77	3.19	<10	0.18	1727	2	0.01	58	820	24	<5	<20	26	0.09	<10	26	<10	21	90
41	L20100N 4500E	10	<0.2	1.95	10	105	10	0.36	<1	21	65	51	3.48	<10	1.05	371	1	0.01	44	300	14	<5	<20	5	0.32	<10	27	<10	27	67
42	L20100N 4525E	5	<0.2	1.59	10	155	10	0.32	<1	20	55	36	3.28	<10	0.82	786	1	0.01	34	410	14	<5	<20	7	0.25	<10	38	<10	18	64
43	L20100N 4550E	5	<0.2	1.71	5	235	10	0.70	<1	19	57	43	2.98	<10	0.94	1568	<1	0.01	37	500	16	<5	<20	13	0.19	<10	37	<10	31	69
44	L20100N 4575E	<5	0.7	1.57	<5	175	10	0.38	<1	14	41	30	3.29	<10	0.39	303	2	0.01	19	390	16	<5	<20	9	0.19	<10	35	<10	28	67
45	L20100N 4600E	10	0.8	1.48	10	255	<5	1.70	<1	9	39	55	1.50	<10	0.26	1356	<1	0.02	21	1030	14	<5	<20	46	0.04	<10	30	<10	82	42
46	L20100N 4625E	5	0.2	1.16	<5	140	10	0.17	<1	14	44	20	3.34	<10	0.42	407	1	0.01	21	330	12	<5	<20	5	0.27	<10	41	<10	11	56
47	L20100N 4650E	80	<0.2	1.59	15	180	5	0.31	<1	21	57	42	3.48	<10	0.81	642	<1	<0.01	41	440	18	<5	<20	17	0.21	<10	35	<10	19	87
48	L20100N 4675E	10	<0.2	1.86	10	225	5	0.41	<1	24	69	56	3.78	<10	1.00	771	<1	0.01	43	480	16	<5	<20	12	0.23	<10	48	<10	27	75
49	L20100N 4700E	10	<0.2	1.66	10	280	10	0.50	<1	23	62	54	3.65	<10	0.90	875	1	0.01	40	640	20	<5	<20	12	0.17	<10	47	<10	24	91
50	L20100N 4725E	5	<0.2	1.93	5	205	10	0.40	<1	21	60	44	3.71	<10	0.87	464	1	0.01	39	410	16	<5	<20	14	0.23	<10	41	<10	18	72
51	L20100N 4750E	5	<0.2	1.97	<5	190	10	0.42	<1	20	63	36	3.88	<10	1.01	442	1	0.01	43	410	14	<5	<20	22	0.24	<10	43	<10	18	92
52	L20100N 4775E	10	0.2	1.81	<5	205	10	0.37	<1	22	61	40	3.68	<10	0.92	624	1	0.01	41	460	18	<5	<20	10	0.22	<10	38	<10	20	81
53	L20100N 4800E	15	0.2	1.29	<5	445	5	0.45	<1	14	40	19	3.39	<10	0.55	1107	2	0.01	24	620	14	<5	<20	16	0.18	<10	49	<10	4	109
54	L20100N 4825E	<5	0.6	0.58	<5	235	<5	0.30	<1	10	22	15	2.11	<10	0.17	910	2	0.01	13	640	14	<5	<20	11	0.07	<10	35	<10	1	81
55	L20100N 4850E	10	0.3	1.26	15	245	10	0.28	<1	13	38	23	3.34	<10	0.47	379	4	<0.01	26	440	18	<5	<20	11	0.18	<10	39	<10	6	97
56	L20100N 4875E	10	0.5	1.16	10	190	5	0.35	<1	14	35	23	2.81	<10	0.45	740	2	0.01	23	700	18	<5	<20	13	0.17	<10	34	<10	7	84
57	L20100N 4900E	20	0.4	1.71	15	170	10	0.39	<1	18	51	35	3.48	<10	0.70	611	2	0.01	42	760	26	<5	<20	9	0.15	<10	46	<10	13	105
58	L20100N 4925E	65	0.4	0.92	65	195	<5	0.30	<1	28	25	61	4.75	<10	0.29	1151	3	<0.01	93	770	26	<5	<20	16	0.05	<10	27	<10	<1	156
59	L20100N 4950E	20	0.7	0.44	30	90	<5	0.15	<1	8	10	18	2.36	<10	0.05	260	2	<0.01	23	620	18	<5	<20	6	0.04	<10	26	<10	<1	86
60	L20100N 4975E	20	0.3	0.95	35	135	5	0.14	<1	17	20	17	3.18	<10	0.16	1272	2	0.01	23	1240	20	<5	<20	5	0.09	<10	23	<10	<1	75
61	L20100N 5025E	355	0.7	0.45	105	100	<5	0.06	<1	9	13	22	2.92	<10	0.05	930	2	<0.01	24	660	48	<5	<20	4	0.04	<10	35	<10	<1	58
62	L20100N 5050E	85	0.6	0.68	275	85	5	0.07	<1	28	12	42	5.40	<10	0.07	881	4	<0.01	92	770	24	<5	<20	9	0.02	<10	25	<10	<1	162
63	L20100N 5075E	45	1.5	1.73	90	75	<5	0.34	<1	22	13	67	3.05	<10	0.15	2118	2	0.02	93	1000	32	<5	<20	35	0.05	<10	17	<10	25	102
64	L20100N 5100E	10	0.3	0.29	40	75	<5	0.15	<1	8	7	21	2.80	<10	0.03	160	2	<0.01	32	500	14	<5	<20	9	0.02	<10	27	<10	<1	68
65	L20100N 5125E	25	1.5	0.82	75	255	<5	0.48	<1	23	16	46	4.12	<10	0.20	1448	3	0.01	105	920	34	<5	<20	44	<0.01	<10	22	<10	19	116

N/	DTA	URC	PCF	ICAT	ANA	SAK	4-149	DOT	LAB	ORY																				
Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
66	L20100N 5150E	5	0.4	0.34	30	60	<5	0.05	<1	8	6	20	2.68	<10	0.01	165	2	<0.01	31	470	10	<5	<20	5	0.02	<10	26	<10	<1	66
67	L20100N 5175E	5	0.3	0.69	25	85	5	0.04	<1	13	14	14	3.32	<10	0.04	566	3	<0.01	35	610	18	<5	<20	3	0.04	<10	34	<10	<1	65
68	L20100N 5200E	15	0.5	0.74	35	370	5	0.16	<1	13	17	20	3.48	<10	0.10	1059	2	<0.01	35	850	16	<5	<20	9	0.04	<10	32	<10	<1	98
69	L20100N 5225E	10	0.7	0.96	25	160	10	0.29	<1	14	28	18	2.95	<10	0.24	1760	2	<0.01	26	1140	20	<5	<20	7	0.08	<10	31	<10	<1	86
70	L20100N 5250E	10	2.3	1.82	45	445	<5	0.62	<1	27	40	75	4.04	10	0.28	2202	2	0.02	141	850	36	<5	<20	57	0.03	<10	33	<10	96	120
71	L20100N 5275E	10	1.7	0.97	20	80	<5	0.06	<1	25	18	36	3.94	<10	0.05	1924	2	<0.01	40	820	22	<5	<20	5	0.02	<10	26	<10	<1	82
72	L20100N 5300E	10	0.5	0.82	15	90	5	0.09	<1	17	24	19	3.60	<10	0.15	929	2	0.01	26	690	22	<5	<20	5	0.07	<10	30	<10	<1	69
73	L20100N 5325E	5	0.2	1.08	35	145	5	0.07	<1	19	36	24	4.12	<10	0.30	685	3	<0.01	43	630	20	<5	<20	2	0.05	<10	48	<10	<1	91
74	L20100N 5350E	10	1.9	1.76	55	385	<5	0.10	<1	41	49	95	5.10	<10	0.21	1477	4	0.01	97	1120	42	<5	<20	9	0.02	<10	49	<10	17	134
75	L20100N 5375E	5	0.6	0.77	35	175	<5	0.09	<1	23	27	28	4.24	<10	0.13	2261	3	<0.01	30	770	26	<5	<20	3	0.06	<10	45	<10	<1	80
76	L20100N 5400E	20	0.7	0.56	20	145	<5	0.18	<1	11	19	22	2.69	<10	0.11	1155	1	<0.01	25	700	16	<5	<20	8	0.05	<10	34	<10	<1	67
77	L20100N 5425E	15	0.5	1.23	45	95	10	0.12	<1	27	44	51	5.65	<10	0.48	653	3	<0.01	66	1110	26	<5	<20	2	0.09	<10	40	<10	<1	106
78	L20100N 5450E	10	1.0	1.76	25	380	<5	0.39	<1	27	45	53	4.03	<10	0.33	2738	2	0.01	83	1170	34	<5	<20	33	0.02	<10	42	<10	28	145
79	L20100N 5475E	15	0.6	1.36	15	145	<5	0.08	<1	10	27	24	3.77	<10	0.15	348	3	0.01	34	720	26	<5	<20	5	0.05	<10	46	<10	<1	91
80	L20100N 5500E	5	0.4	0.84	5	90	5	0.06	<1	16	19	13	2.86	<10	0.08	1766	2	0.01	15	880	18	<5	<20	2	0.10	<10	29	<10	<1	54

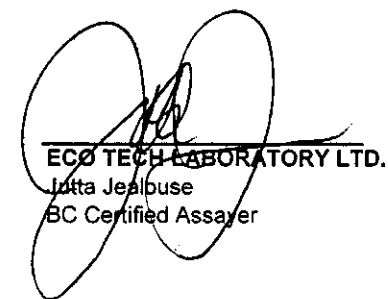
QC DATA:

Repeat:

1	L20000N 4500E	5	0.3	1.58	10	170	5	0.58	<1	11	36	43	2.69	<10	0.56	271	2	0.01	22	310	14	<5	<20	19	0.14	<10	29	<10	36	91
10	L20000N 4725E	5	1.0	2.13	15	525	<5	0.55	<1	27	56	79	2.99	<10	0.66	943	1	0.01	57	850	24	<5	<20	57	0.12	<10	48	<10	65	106
15	L20000N 4850E	75	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-
16	L20000N 4875E	405	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-
17	L20000N 4900E	300	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-
18	L20000N 4925E	90	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-
19	L20000N 4950E	120	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-
19	L20000N 4950E	25	1.1	1.09	75	215	5	0.49	<1	17	18	26	3.15	<10	0.19	1135	1	0.02	47	810	26	<5	<20	38	0.06	<10	29	<10	11	124
20	L20000N 4975E	40	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-
21	L20000N 5025E	100	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-
22	L20000N 5050E	310	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-
23	L20000N 5075E	55	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-
24	L20000N 5100E	155	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-
25	L20000N 5125E	510	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-
26	L20000N 5150E	30	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-
27	L20000N 5175E	20	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-
28	L20000N 5200E	45	1.8	0.64	70	60	5	0.05	<1	8	11	19	3.28	<10	0.07	181	3	<0.01	27	650	20	<5	<20	3	0.05	<10	23	<10	<1	55
36	L20000N 5400E	5	0.2	0.85	15	100	<5	0.11	<1	15	20	17	3.52	<10	0.13	1274	2	0.01	27	740	16	<5	<20	4	0.09	<10	28	<10	<1	78
45	L20100N 4600E	5	0.7	1.43	5	245	<5	1.63	<1	9	38	52	1.48	<10	0.27	1308	<1	0.02	20	960	14	<5	<20	44	0.04	<10	29	<10	80	41
54	L20100N 4825E	5	0.5	0.58	<5	235	5	0.27	<1	11	22	15	2.22	<10	0.16	939	2	0.01	14	640	16	<5	<20	11	0.08	<10	37	<10	1	84
61	L20100N 5025E	400	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-
63	L20100N 5075E	15	1.6	1.77	90	75	<5	0.35	<1	22	14	58	2.88	<10	0.16	2253	2	0.02	91	1070	34	<5	<20	35	0.05	<10	17	<10	26	96
71	L20100N 5275E	15	1.8	0.92	20	75	<5	0.05	<1	21	17	32	3.89	<10	0.04	1885	2	<0.01	40	740	20	<5	<20	2	0.02	<10	26	<10	<1	74

Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn	
Standard:																															
GEO'04		140	1.4	1.44	55	140	<5	1.36	<1	17	59	84	3.19	<10	0.76	582	<1	0.02	27	710	22	<5	<20	55	0.10	<10	59	<10	10	77	
GEO'04		140	1.6	1.50	65	150	<5	1.45	<1	18	62	86	3.36	<10	0.78	628	<1	0.02	30	710	20	<5	<20	59	0.10	<10	59	<10	10	76	
GEO'04		140	1.4	1.46	65	145	<5	1.44	<1	18	61	84	3.34	<10	0.77	618	<1	0.02	29	730	22	<5	<20	57	0.11	<10	58	<10	11	74	

J/jm
#1491
LS/04


ECO TECH LABORATORY LTD.
 Jutta Jealbusse
 BC Certified Assayer

ECO TECH LABORATORY LTD.
10041 Dallas Drive
KAMLOOPS, B.C.
V2C 6T4

ICP CERTIFICATE OF ANALYSIS AK 2004-1495

NAVASOTA RESOURCES
#207 141 VICTORIA STREET
KAMLOOPS, BC
V2C 1Z5

Phone: 250-573-5700
Fax : 250-573-4557

No. of samples received: 80
Sample type: Soil
Project #: Not Indicated
Shipment #: Not Indicated

Values in ppm unless otherwise reported

Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
1	L20200N 4500E	5	0.5	2.61	15	195	<5	0.59	<1	15	40	28	2.31	<10	0.57	1005	1	0.02	25	580	20	<5	<20	16	0.08	<10	29	<10	39	63
2	L20200N 4525E	10	0.6	2.45	10	215	<5	0.54	<1	17	53	40	2.74	<10	0.62	893	2	0.01	29	560	22	<5	<20	14	0.08	<10	38	<10	43	66
3	L20200N 4550E	<5	0.4	0.92	<5	120	10	0.13	<1	8	28	13	2.38	<10	0.26	201	2	<0.01	12	320	16	<5	<20	5	0.11	<10	46	<10	1	39
4	L20200N 4575E	<5	0.2	1.12	<5	145	<5	0.16	<1	12	34	14	2.83	<10	0.39	689	2	<0.01	16	370	16	<5	<20	5	0.12	<10	49	<10	2	52
5	L20200N 4600E	5	0.4	1.97	5	160	<5	0.65	<1	17	56	34	2.88	<10	0.90	644	1	<0.01	33	420	16	<5	<20	17	0.09	<10	35	<10	33	48
6	L20200N 4625E	5	0.2	1.71	10	130	10	0.27	<1	17	48	31	3.43	<10	0.81	382	2	<0.01	32	270	20	<5	<20	8	0.14	<10	41	<10	10	60
7	L20200N 4650E	10	0.3	1.37	<5	95	10	0.15	<1	14	41	23	3.61	<10	0.50	266	2	<0.01	18	350	16	<5	<20	7	0.16	<10	34	<10	7	49
8	L20200N 4675E	<5	0.2	1.20	<5	145	10	0.19	<1	11	37	20	2.78	<10	0.40	389	2	0.01	16	310	16	<5	<20	10	0.12	<10	35	<10	4	52
9	L20200N 4700E	<5	0.3	1.38	<5	130	<5	0.15	<1	9	30	34	2.64	<10	0.24	131	2	<0.01	15	270	16	<5	<20	12	0.09	<10	34	<10	16	60
10	L20200N 4725E	5	0.3	1.37	5	150	5	0.22	<1	11	32	24	2.77	<10	0.44	565	2	<0.01	18	510	18	<5	<20	12	0.09	<10	36	<10	3	62
11	L20200N 4750E	<5	0.3	0.45	10	125	<5	0.21	<1	7	10	19	2.17	<10	0.11	241	2	<0.01	16	510	18	<5	<20	23	0.03	<10	24	<10	2	65
12	L20200N 4775E	20	0.5	0.93	<5	345	<5	1.14	1	5	18	19	1.69	<10	0.26	894	2	<0.01	14	830	22	<5	<20	48	0.03	<10	23	<10	5	117
13	L20200N 4800E	5	0.7	1.45	5	435	<5	0.78	1	16	29	32	2.47	<10	0.44	938	2	<0.01	31	1030	28	<5	<20	35	0.03	<10	37	<10	15	191
14	L20200N 4825E	30	0.6	1.56	25	130	10	0.27	<1	16	48	37	3.49	<10	0.77	392	3	<0.01	32	440	28	<5	<20	10	0.12	<10	41	<10	6	92
15	L20200N 4850E	65	0.7	1.12	15	165	<5	0.20	<1	12	33	29	3.22	<10	0.34	626	3	<0.01	23	570	58	<5	<20	15	0.07	<10	50	<10	<1	98
16	L20200N 4875E	25	0.4	1.10	20	230	5	0.16	<1	15	32	23	3.27	<10	0.33	1070	4	<0.01	22	540	36	<5	<20	11	0.05	<10	52	<10	<1	118
17	L20200N 4900E	30	0.4	1.10	20	135	<5	0.14	<1	14	31	23	3.32	<10	0.37	727	3	<0.01	25	740	22	<5	<20	4	0.06	<10	46	<10	<1	85
18	L20200N 4925E	20	0.4	1.09	30	170	<5	0.13	<1	17	29	27	3.44	<10	0.29	1121	3	<0.01	32	570	24	<5	<20	7	0.05	<10	47	<10	<1	84
19	L20200N 4950E	10	0.8	0.80	15	95	<5	0.10	<1	10	20	15	2.88	<10	0.16	635	3	<0.01	19	590	16	<5	<20	5	0.05	<10	39	<10	<1	52
20	L20200N 4975E	10	0.8	1.18	10	120	5	0.11	<1	10	28	15	3.11	<10	0.24	314	2	<0.01	19	530	16	<5	<20	4	0.07	<10	41	<10	<1	62
21	L20200N 5025E	40	2.6	2.07	135	460	<5	0.40	<1	34	41	119	5.06	10	0.42	3327	3	<0.01	210	1440	50	<5	<20	53	0.01	<10	38	<10	128	188
22	L20200N 5050E	50	0.8	0.75	155	125	<5	0.28	<1	18	16	34	3.78	<10	0.14	789	3	<0.01	58	710	22	<5	<20	13	0.02	<10	30	<10	<1	103
23	L20200N 5075E	35	0.6	0.86	50	115	5	0.21	<1	13	27	28	3.71	<10	0.28	527	3	<0.01	39	750	18	<5	<20	9	0.03	<10	39	<10	<1	79
24	L20200N 5100E	10	1.3	1.45	35	90	<5	0.16	<1	11	13	23	3.08	<10	0.09	925	2	<0.01	17	1210	20	<5	<20	9	0.04	<10	20	<10	<1	55
25	L20200N 5125E	10	1.6	0.94	10	55	<5	0.06	<1	7	14	11	2.24	<10	0.07	457	2	<0.01	10	530	14	<5	<20	4	0.07	<10	29	<10	<1	27

Et #	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
26	L20200N 5150E	10	1.0	1.67	15	130	<5	0.17	<1	18	46	24	3.45	<10	0.34	1079	1	<0.01	26	640	16	<5	<20	10	0.12	<10	58	<10	2	73
27	L20200N 5175E	15	1.0	1.16	15	185	<5	0.16	<1	9	22	26	2.86	<10	0.10	393	3	<0.01	20	460	18	<5	<20	14	0.05	<10	39	<10	1	55
28	L20200N 5200E	75	0.6	0.89	20	95	5	0.10	<1	9	23	15	3.23	<10	0.14	648	3	<0.01	16	1690	18	<5	<20	5	0.04	<10	40	<10	<1	41
29	L20200N 5225E	10	0.6	1.83	30	130	10	0.14	<1	16	35	27	3.48	<10	0.37	485	3	<0.01	39	880	22	<5	<20	5	0.04	<10	33	<10	2	86
30	L20200N 5250E	20	0.5	1.74	25	120	<5	0.11	<1	18	35	21	3.38	<10	0.29	948	3	<0.01	31	1150	18	<5	<20	4	0.03	<10	39	<10	<1	76
31	L20200N 5275E	5	0.5	0.51	5	80	<5	0.05	<1	12	12	11	1.72	<10	0.06	1825	1	<0.01	9	840	20	<5	<20	3	0.03	<10	27	<10	<1	31
32	L20200N 5300E	5	1.0	1.34	25	125	<5	0.06	<1	23	31	43	3.52	<10	0.24	2438	3	<0.01	35	1250	30	<5	<20	5	0.02	<10	35	<10	<1	64
33	L20200N 5325E	10	0.6	0.79	15	125	5	0.12	<1	11	22	24	2.84	<10	0.21	787	2	<0.01	27	600	20	<5	<20	6	0.04	<10	35	<10	<1	56
34	L20200N 5350E	10	0.2	1.51	10	110	10	0.18	<1	11	30	14	2.80	<10	0.26	513	3	<0.01	17	820	18	<5	<20	8	0.07	<10	41	<10	<1	51
35	L20200N 5375E	5	0.3	0.64	10	125	5	0.10	<1	8	22	11	2.66	<10	0.16	397	2	<0.01	17	810	16	<5	<20	5	0.07	<10	42	<10	<1	39
36	L20200N 5400E	5	0.5	0.91	10	110	<5	0.10	<1	16	28	14	3.11	<10	0.27	1211	2	<0.01	26	640	16	<5	<20	6	0.04	<10	37	<10	<1	63
37	L20200N 5425E	15	0.3	0.73	20	195	<5	0.20	<1	16	26	25	3.30	<10	0.26	2622	2	<0.01	38	760	20	<5	<20	13	0.02	<10	33	<10	<1	86
38	L20200N 5450E	15	0.3	1.78	20	130	<5	0.12	<1	18	37	28	3.55	<10	0.40	1340	3	<0.01	39	1050	22	<5	<20	5	0.03	<10	38	<10	<1	94
39	L20200N 5475E	30	0.5	1.09	15	100	5	0.10	<1	17	34	20	3.36	<10	0.35	937	2	<0.01	35	880	20	<5	<20	4	0.05	<10	41	<10	<1	66
40	L20200N 5500E	10	0.7	0.98	15	100	5	0.10	<1	12	31	18	3.62	<10	0.27	518	3	<0.01	28	860	18	<5	<20	4	0.05	<10	45	<10	<1	64
41	L20300N 4500E	5	0.3	1.27	<5	150	<5	0.23	<1	11	45	20	2.35	<10	0.36	500	2	<0.01	19	590	20	<5	<20	8	0.05	<10	37	<10	10	58
42	L20300N 4525E	5	0.2	1.80	10	135	<5	0.21	<1	13	40	18	2.56	<10	0.32	762	2	<0.01	19	580	20	<5	<20	7	0.05	<10	45	<10	8	67
43	L20300N 4550E	5	0.2	1.98	10	100	<5	0.23	<1	14	30	18	2.33	<10	0.30	628	2	<0.01	18	400	22	<5	<20	8	0.06	<10	29	<10	19	54
44	L20300N 4575E	<5	0.4	1.51	5	100	<5	0.50	<1	12	23	20	2.21	<10	0.24	442	2	0.01	14	550	24	<5	<20	13	0.06	<10	23	<10	35	46
45	L20300N 4600E	<5	<0.2	1.76	5	145	<5	0.21	<1	13	27	41	2.61	<10	0.30	371	2	<0.01	16	530	24	<5	<20	10	0.11	<10	43	<10	17	46
46	L20300N 4625E	5	0.3	1.59	<5	100	5	0.14	<1	13	37	19	2.99	<10	0.47	366	2	<0.01	18	350	16	<5	<20	6	0.10	<10	30	<10	5	47
47	L20300N 4650E	5	0.4	1.19	<5	145	5	0.23	<1	10	30	14	3.25	<10	0.24	186	2	<0.01	11	280	18	<5	<20	13	0.13	<10	31	<10	7	37
48	L20300N 4675E	<5	0.2	0.75	<5	90	5	0.07	<1	8	24	11	2.36	<10	0.19	104	1	<0.01	11	240	14	<5	<20	3	0.11	<10	29	<10	3	29
49	L20300N 4700E	5	0.3	0.80	<5	95	5	0.15	<1	10	29	14	2.61	<10	0.34	169	2	<0.01	14	330	26	<5	<20	5	0.14	<10	45	<10	4	76
50	L20300N 4725E	5	1.2	2.46	15	170	<5	1.13	1	16	35	35	2.22	<10	0.48	1615	1	<0.01	39	1570	30	<5	<20	39	0.03	<10	34	<10	60	195
51	L20300N 4750E	10	0.3	1.40	<5	135	10	0.20	<1	17	37	19	3.27	<10	0.52	776	2	<0.01	19	330	26	<5	<20	11	0.11	<10	43	<10	8	67
52	L20300N 4775E	5	0.4	1.76	<5	140	5	0.23	<1	22	37	34	2.95	<10	0.39	812	2	<0.01	21	450	32	<5	<20	21	0.07	<10	50	<10	33	63
53	L20300N 4800E	5	0.3	1.88	5	140	5	0.19	<1	20	41	35	3.35	<10	0.47	616	3	<0.01	23	380	22	<5	<20	15	0.09	<10	51	<10	23	59
54	L20300N 4825E	5	0.3	1.74	5	185	5	0.48	<1	21	52	34	3.38	<10	0.82	543	2	<0.01	36	330	22	<5	<20	40	0.08	<10	42	<10	19	70
55	L20300N 4850E	5	0.9	1.53	5	240	<5	0.74	1	16	32	70	2.50	<10	0.35	1436	3	<0.01	33	930	32	<5	<20	79	0.03	<10	41	<10	47	105
56	L20300N 4875E	10	0.3	0.78	10	185	<5	0.44	<1	11	24	36	2.88	<10	0.19	533	3	<0.01	21	670	42	<5	<20	34	0.03	<10	45	<10	5	86
57	L20300N 4900E	85	0.6	1.13	15	165	<5	0.24	<1	14	30	31	2.99	<10	0.33	671	3	<0.01	27	490	60	<5	<20	16	0.05	<10	39	<10	5	125
58	L20300N 4925E	105	1.0	1.26	25	190	<5	0.26	<1	16	29	69	3.14	<10	0.29	909	3	<0.01	31	820	326	<5	<20	21	0.03	<10	41	<10	18	237
59	L20300N 4950E	15	1.3	0.73	15	155	<5	0.16	<1	11	24	20	2.97	<10	0.21	717	2	<0.01	22	800	26	<5	<20	9	0.04	<10	44	<10	<1	85
60	L20300N 4975E	20	0.7	0.40	20	305	<5	0.05	<1	5	11	15	1.86	<10	0.05	630	2	<0.01	14	510	20	<5	<20	6	0.03	<10	31	<10	<1	47
61	L20300N 5025E	10	0.6	0.51	35	165	<5	0.07	<1	6	12	18	2.22	<10	0.07	158	2	<0.01	21	580	26	<5	<20	11	0.02	<10	32	<10	<1	47
62	L20300N 5050E	25	1.2	1.55	70	170	<5	0.15	<1	23	23	35	3.63	<10	0.27	1302	2	<0.01	50	940	38	<5	<20	11	0.05	<10	26	<10	<1	103
63	L20300N 5075E	30	0.7	0.76	40	75	<5	0.11	<1	13	21	20	3.04	<10	0.17	610	3	<0.01	25	590	22	<5	<20	5	0.05	<10	36	<10	<1	58
64	L20300N 5100E	20	0.5	1.37	35	65	10	0.16	<1	16	43	20	3.58	<10	0.57	439	3	<0.01	39	680	20	<5	<20	4	0.07	<10	30	<10	<1	76
65	L20300N 5125E	10	0.8	1.02	10	50	<5	0.06	<1	8	19	11	2.10	<10	0.13	353	2	<0.01	12	820	16	<5	<20	<1	0.04	<10	27	<10	<1	34

Et #	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
66	L20300N 5150E	35	0.6	1.41	45	175	<5	0.10	<1	18	38	34	3.82	<10	0.37	857	3	<0.01	48	500	24	<5	<20	5	0.03	<10	43	<10	<1	87
67	L20300N 5175E	75	0.8	1.35	35	220	<5	0.13	<1	21	35	32	3.81	<10	0.37	1048	2	<0.01	48	680	24	<5	<20	6	0.02	<10	42	<10	<1	89
68	L20300N 5200E	20	1.3	1.86	35	110	10	0.18	<1	19	43	30	4.11	<10	0.52	487	3	<0.01	43	970	62	<5	<20	6	0.05	<10	41	<10	<1	111
69	L20300N 5225E	20	0.9	1.52	25	95	5	0.12	<1	14	34	18	3.83	<10	0.32	526	3	<0.01	31	1200	20	<5	<20	3	0.05	<10	36	<10	<1	81
70	L20300N 5250E	20	0.5	1.11	15	75	<5	0.08	<1	10	23	12	2.72	<10	0.17	429	2	<0.01	19	680	18	<5	<20	2	0.04	<10	40	<10	<1	48
71	L20300N 5275E	20	0.7	1.51	45	105	<5	0.30	<1	23	44	35	4.29	<10	0.48	489	4	<0.01	60	970	36	<5	<20	10	0.06	<10	36	<10	<1	128
72	L20300N 5300E	15	0.6	1.23	25	90	5	0.23	<1	16	46	24	4.47	<10	0.47	317	5	<0.01	47	1490	32	<5	<20	7	0.08	<10	36	<10	<1	94
73	L20300N 5325E	5	1.1	1.58	35	115	<5	0.08	<1	27	33	37	3.61	<10	0.25	2902	3	<0.01	35	1630	46	<5	<20	4	0.04	<10	28	<10	<1	90
74	L20300N 5350E	5	0.8	1.17	25	70	<5	0.10	<1	10	22	17	3.29	<10	0.12	477	3	<0.01	24	930	42	<5	<20	9	0.03	<10	31	<10	<1	57
75	L20300N 5375E	10	0.8	1.21	30	105	10	0.15	<1	15	43	22	4.35	<10	0.34	480	4	<0.01	42	940	36	<5	<20	3	0.06	<10	44	<10	<1	86
76	L20300N 5400E	15	0.6	1.50	30	125	<5	0.19	<1	22	45	32	4.13	<10	0.47	881	3	<0.01	58	900	44	<5	<20	5	0.06	<10	36	<10	1	105
77	L20300N 5425E	5	0.8	0.73	10	70	5	0.07	<1	9	22	10	2.77	<10	0.13	454	3	<0.01	17	510	26	<5	<20	1	0.07	<10	39	<10	<1	47
78	L20300N 5450E	5	0.8	1.48	20	60	<5	0.05	<1	23	36	19	3.52	<10	0.35	1499	3	<0.01	37	1100	42	<5	<20	3	0.03	<10	31	<10	<1	88
79	L20300N 5475E	15	1.0	0.67	20	65	5	0.10	<1	12	23	18	3.50	<10	0.18	508	3	<0.01	25	680	26	<5	<20	4	0.07	<10	38	<10	<1	61
80	L20300N 5500E	5	1.3	1.77	20	125	10	0.14	<1	20	42	20	4.15	<10	0.37	692	3	<0.01	38	1140	36	<5	<20	6	0.06	<10	41	<10	<1	116

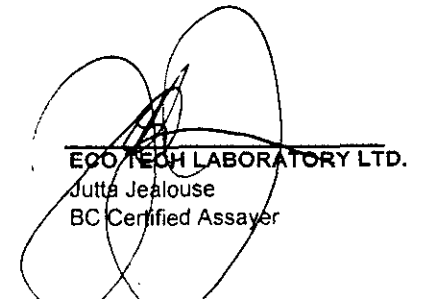
QC DATA:

Repeat:

1	L20200N 4500E	<5	0.5	2.66	10	190	<5	0.61	<1	15	44	28	2.31	<10	0.61	1029	<1	0.02	26	580	20	<5	<20	16	0.08	<10	30	<10	40	65
10	L20200N 4725E	5	0.3	1.37	5	150	5	0.22	<1	11	33	23	2.84	<10	0.46	592	2	<0.01	20	510	18	<5	<20	13	0.09	<10	32	<10	3	64
19	L20200N 4950E	10	0.8	0.84	10	100	<5	0.10	<1	10	20	20	3.09	<10	0.14	634	3	<0.01	23	620	20	<5	<20	6	0.04	<10	38	<10	<1	57
28	L20200N 5200E	5	0.5	0.90	20	95	<5	0.10	<1	9	23	15	3.19	<10	0.13	654	2	<0.01	14	1710	16	<5	<20	5	0.09	<10	47	<10	<1	40
36	L20200N 5400E	5	0.5	0.95	10	110	10	0.11	<1	16	30	14	3.16	<10	0.27	1232	2	<0.01	26	700	18	<5	<20	5	0.04	<10	36	<10	<1	66
45	L20300N 4600E	<5	0.5	1.79	5	145	<5	0.23	<1	13	28	40	2.65	<10	0.32	378	2	<0.01	17	560	22	<5	<20	10	0.09	<10	40	<10	16	48
54	L20300N 4825E	5	0.3	1.78	<5	190	5	0.49	<1	21	53	34	3.48	<10	0.85	552	1	<0.01	36	360	22	<5	<20	41	0.09	<10	44	<10	18	71
63	L20300N 5075E	25	0.8	0.76	40	75	5	0.11	<1	13	21	21	3.05	<10	0.16	582	3	<0.01	25	600	22	<5	<20	7	0.05	<10	35	<10	<1	56
71	L20300N 5275E	10	0.7	1.51	45	105	<5	0.30	<1	21	43	29	4.04	<10	0.48	442	4	<0.01	56	940	34	<5	<20	9	0.07	<10	36	<10	2	118

Standard:

3EO'04	130	1.5	1.50	55	145	<5	1.31	<1	20	58	85	3.09	<10	0.81	571	<1	0.02	28	630	24	<5	<20	54	0.06	<10	60	<10	11	73
3EO'04	130	1.4	1.48	50	145	<5	1.29	<1	20	57	86	3.06	<10	0.80	564	<1	0.02	29	650	24	<5	<20	55	0.06	<10	61	<10	11	74
3EO'04	140	1.5	1.48	65	145	<5	1.45	<1	18	60	84	3.42	<10	0.80	611	<1	0.02	31	790	22	<5	<20	54	0.10	<10	61	<10	11	76


ECO TECH LABORATORY LTD.
 Jutta Jealous
 BC Certified Assayer

ECO TECH LABORATORY LTD.
10041 Dallas Drive
KAMLOOPS, B.C.
V2C 6T4

ICP CERTIFICATE OF ANALYSIS AK 2004-1497

NAVASOTA RESOURCES
#207 141 VICTORIA STREET
KAMLOOPS, BC
V2C 1Z5

Phone: 250-573-5700

Fax : 250-573-4557

No. of samples received: 80

Sample type: Soil

Project #: Not Indicated

Shipment #: Not Indicated

Values in ppm unless otherwise reported

Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
1	L20400N 4500E	15	<0.2	0.65	15	95	<5	0.14	<1	8	11	9	2.18	<10	0.15	503	2	<0.01	18	420	14	<5	<20	6	0.04	<10	36	<10	<1	34
2	L20400N 4525E	5	<0.2	1.15	25	140	5	0.11	<1	17	43	15	4.01	<10	0.29	889	3	<0.01	37	260	12	<5	<20	6	0.06	<10	57	<10	<1	54
3	L20400N 4550E	25	<0.2	2.13	<5	85	10	0.19	<1	15	56	24	3.44	<10	0.75	278	2	<0.01	30	450	18	<5	<20	5	0.18	<10	44	<10	11	56
4	L20400N 4575E	<5	<0.2	1.39	<5	85	10	0.15	<1	13	44	15	3.31	<10	0.56	214	2	<0.01	20	260	16	<5	<20	4	0.19	<10	45	<10	5	48
5	L20400N 4600E	<5	<0.2	1.38	<5	100	5	0.17	<1	12	36	13	2.84	<10	0.46	441	2	<0.01	18	290	18	<5	<20	4	0.11	<10	37	<10	4	55
6	L20400N 4625E	<5	0.2	1.46	<5	85	5	0.19	<1	26	37	21	2.51	<10	0.48	1247	2	<0.01	26	430	20	<5	<20	6	0.07	<10	48	<10	10	57
7	L20400N 4650E	5	0.2	1.14	5	75	10	0.12	<1	14	81	14	3.20	<10	0.48	454	2	<0.01	28	330	16	<5	<20	6	0.14	<10	67	<10	<1	59
8	L20400N 4675E	<5	0.2	0.97	<5	85	5	0.06	<1	9	31	14	2.60	<10	0.24	348	2	<0.01	14	280	16	<5	<20	4	0.11	<10	51	<10	<1	44
9	L20400N 4700E	<5	0.5	1.58	<5	65	5	0.36	<1	12	26	22	2.25	<10	0.21	453	2	0.01	13	340	18	<5	<20	10	0.08	<10	28	<10	15	48
10	L20400N 4725E	5	0.7	2.31	10	130	<5	1.41	1	12	34	47	2.14	<10	0.38	1002	1	0.02	19	910	34	<5	<20	61	0.04	<10	31	<10	35	102
11	L20400N 4750E	5	1.1	1.54	5	75	<5	0.86	1	10	23	32	2.39	<10	0.23	209	2	0.01	15	560	18	<5	<20	34	0.05	<10	33	<10	21	74
12	L20400N 4775E	10	1.2	1.99	5	135	<5	0.91	2	16	24	41	2.45	<10	0.29	1218	1	0.01	27	780	22	<5	<20	42	0.04	<10	27	<10	23	140
13	L20400N 4800E	5	0.9	1.73	5	145	<5	0.64	1	17	31	33	2.81	<10	0.41	444	2	0.01	41	420	24	<5	<20	31	0.07	<10	30	<10	31	177
14	L20400N 4825E	15	0.5	1.70	10	325	10	0.29	<1	14	45	28	3.48	<10	0.66	303	3	<0.01	39	360	38	<5	<20	12	0.12	<10	36	<10	10	113
15	L20400N 4850E	10	0.3	1.00	10	230	5	0.30	<1	11	35	25	2.99	<10	0.36	558	4	<0.01	23	560	60	<5	<20	25	0.06	<10	42	<10	<1	106
16	L20400N 4875E	40	0.2	1.04	20	245	<5	0.19	<1	13	31	39	2.95	<10	0.32	864	3	<0.01	28	770	60	<5	<20	19	0.04	<10	47	<10	7	111
17	L20400N 4900E	25	0.8	1.00	20	355	<5	0.35	<1	16	26	42	3.16	<10	0.29	1241	3	<0.01	36	840	38	<5	<20	33	0.03	<10	40	<10	20	128
18	L20400N 4925E	20	0.5	0.79	15	395	<5	0.47	<1	14	23	34	2.55	<10	0.29	1770	2	<0.01	34	1050	28	<5	<20	31	0.03	<10	29	<10	3	127
19	L20400N 4950E	10	0.7	0.87	15	200	5	0.28	<1	15	26	26	3.32	<10	0.26	955	3	<0.01	24	820	30	<5	<20	17	0.07	<10	37	<10	<1	95
20	L20400N 4975E	15	1.6	2.04	60	420	<5	0.22	<1	25	46	101	4.09	<10	0.42	1286	2	<0.01	125	690	38	<5	<20	25	0.04	<10	36	<10	86	121
21	L20400N 5025E	475	1.8	1.00	180	125	<5	0.11	<1	24	21	50	4.95	<10	0.20	812	4	<0.01	77	780	40	<5	<20	11	<0.01	<10	36	<10	<1	134
22	L20400N 5050E	5	0.8	0.44	10	100	<5	0.12	<1	6	13	13	1.52	<10	0.10	385	1	<0.01	15	550	24	<5	<20	8	0.02	<10	26	<10	<1	39
23	L20400N 5075E	45	0.8	1.00	25	60	<5	0.05	<1	8	16	15	2.55	<10	0.11	350	2	<0.01	16	630	18	<5	<20	4	0.05	<10	30	<10	<1	34
24	L20400N 5100E	985	0.5	0.60	50	80	5	0.08	<1	10	12	21	3.37	<10	0.09	417	3	<0.01	31	630	20	<5	<20	6	0.02	<10	32	<10	<1	82
25	L20400N 5125E	175	0.6	0.73	40	60	5	0.08	<1	11	11	18	3.35	<10	0.06	316	3	<0.01	33	670	22	<5	<20	4	0.02	<10	29	<10	<1	51

Et #	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
26	L20400N 5150E	50	0.4	0.85	15	95	5	0.14	<1	13	32	15	3.09	<10	0.28	1105	2	<0.01	20	730	18	<5	<20	5	0.07	<10	43	<10	<1	49
27	L20400N 5175E	5	0.4	1.07	5	60	5	0.11	<1	8	25	13	2.38	<10	0.18	379	2	<0.01	12	580	18	<5	<20	2	0.06	<10	36	<10	<1	33
28	L20400N 5200E	10	0.8	1.26	20	90	<5	0.11	<1	13	33	20	3.45	<10	0.27	702	2	<0.01	26	590	18	<5	<20	4	0.07	<10	45	<10	<1	50
29	L20400N 5225E	15	1.0	0.89	15	75	10	0.08	<1	10	22	14	2.82	<10	0.17	322	2	<0.01	21	550	16	<5	<20	2	0.07	<10	40	<10	<1	43
30	L20400N 5250E	10	1.5	1.49	20	105	5	0.12	<1	14	30	17	3.29	<10	0.26	679	3	<0.01	25	760	20	<5	<20	3	0.05	<10	37	<10	<1	66
31	L20400N 5275E	10	2.2	1.86	20	100	10	0.17	<1	17	46	32	3.67	<10	0.45	469	2	<0.01	41	800	22	<5	<20	5	0.07	<10	33	<10	<1	74
32	L20400N 5300E	5	0.6	0.84	20	75	5	0.12	<1	10	21	15	3.55	<10	0.15	521	3	<0.01	22	590	16	<5	<20	5	0.05	<10	48	<10	<1	51
33	L20400N 5325E	10	0.6	1.84	15	85	5	0.11	<1	11	31	13	3.49	<10	0.19	523	3	<0.01	19	610	22	<5	<20	4	0.08	<10	33	<10	<1	51
34	L20400N 5350E	5	2.5	2.45	25	90	<5	0.07	<1	19	18	34	2.82	<10	0.13	1613	2	<0.01	30	1100	30	<5	<20	5	0.04	<10	18	<10	2	67
35	L20400N 5375E	5	1.1	1.18	10	75	5	0.11	<1	10	28	14	3.03	<10	0.23	363	2	<0.01	19	600	18	<5	<20	4	0.05	<10	33	<10	<1	42
36	L20400N 5400E	5	0.6	0.99	20	55	<5	0.06	<1	12	17	11	2.71	<10	0.10	702	2	<0.01	14	750	16	<5	<20	4	0.04	<10	40	<10	<1	37
37	L20400N 5425E	5	0.4	0.27	10	40	<5	0.05	<1	6	9	12	1.89	<10	0.04	261	2	<0.01	14	350	10	<5	<20	4	0.03	<10	28	<10	<1	36
38	L20400N 5450E	5	0.7	1.32	15	60	<5	0.05	<1	13	15	15	2.31	<10	0.08	1202	2	<0.01	11	620	16	<5	<20	4	0.04	<10	30	<10	<1	37
39	L20400N 5475E	20	3.1	1.38	20	100	5	0.14	<1	18	37	21	3.59	<10	0.39	1338	3	<0.01	30	1190	18	<5	<20	4	0.08	<10	37	<10	<1	68
40	L20400N 5500E	5	1.4	1.52	25	130	<5	0.25	<1	19	43	30	3.71	<10	0.52	1234	2	<0.01	45	1120	18	<5	<20	10	0.05	<10	36	<10	<1	96
41	L20500N 4500E	<5	0.2	0.98	<5	90	10	0.20	<1	11	31	18	2.52	<10	0.39	268	2	<0.01	15	410	14	<5	<20	8	0.14	<10	49	<10	8	41
42	L20500N 4525E	<5	0.3	1.74	<5	55	5	0.08	<1	8	24	22	2.84	<10	0.23	151	3	<0.01	9	480	14	<5	<20	4	0.09	<10	39	<10	6	32
43	L20500N 4550E	5	0.2	1.91	<5	75	5	0.10	<1	11	32	17	3.08	<10	0.47	198	2	<0.01	17	330	16	<5	<20	5	0.16	<10	36	<10	9	40
44	L20500N 4575E	5	0.2	1.19	<5	80	5	0.11	<1	11	38	13	2.85	<10	0.39	225	1	<0.01	17	280	14	<5	<20	6	0.15	<10	41	<10	5	35
45	L20500N 4600E	5	0.2	1.43	<5	70	10	0.12	<1	12	44	16	3.52	<10	0.52	196	2	<0.01	18	310	16	<5	<20	4	0.18	<10	46	<10	6	39
46	L20500N 4625E	<5	0.2	1.10	<5	50	10	0.06	<1	8	22	11	3.10	<10	0.17	150	2	<0.01	8	350	14	<5	<20	2	0.13	<10	38	<10	4	24
47	L20500N 4650E	25	0.2	0.71	<5	55	<5	0.08	<1	7	20	13	2.50	<10	0.20	122	2	<0.01	8	480	18	<5	<20	5	0.10	<10	36	<10	<1	26
48	L20500N 4675E	5	0.2	1.23	<5	65	5	0.08	<1	9	30	16	3.09	<10	0.33	211	3	<0.01	12	350	16	<5	<20	4	0.09	<10	48	<10	<1	34
49	L20500N 4700E	10	0.2	1.36	<5	105	5	0.14	<1	15	37	18	3.20	<10	0.54	606	3	<0.01	20	420	22	<5	<20	6	0.09	<10	61	<10	5	50
50	L20500N 4725E	5	0.2	1.36	<5	80	5	0.12	<1	10	27	15	2.92	<10	0.36	332	4	<0.01	17	290	16	<5	<20	6	0.07	<10	55	<10	5	43
51	L20500N 4750E	5	0.4	3.29	20	155	<5	0.51	<1	18	53	36	3.12	<10	0.80	595	3	0.01	44	590	20	<5	<20	18	0.08	<10	46	<10	54	80
52	L20500N 4775E	5	1.0	2.44	15	175	<5	1.38	2	9	32	50	1.65	10	0.35	1092	3	0.01	23	1680	20	<5	<20	61	0.01	<10	32	<10	64	108
53	L20500N 4800E	10	0.6	1.97	10	150	<5	0.69	2	17	31	35	2.38	<10	0.43	775	3	0.01	41	630	50	<5	<20	29	0.04	<10	35	<10	27	239
54	L20500N 4825E	20	1.2	1.82	10	325	<5	0.69	2	17	30	42	2.55	<10	0.42	889	3	0.01	37	620	42	<5	<20	29	0.04	<10	33	<10	30	230
55	L20500N 4850E	15	0.3	2.12	15	220	5	0.43	<1	23	57	37	3.44	<10	1.00	457	3	<0.01	53	340	42	<5	<20	14	0.10	<10	48	<10	20	260
56	L20500N 4875E	10	0.8	1.33	25	275	<5	0.74	3	16	26	36	2.42	<10	0.36	1068	2	<0.01	32	1180	72	<5	<20	33	0.02	<10	34	<10	20	240
57	L20500N 4900E	15	0.3	1.96	15	100	10	0.35	<1	19	56	45	3.30	<10	0.97	409	1	<0.01	41	440	32	<5	<20	6	0.13	<10	36	<10	29	112
58	L20500N 4925E	10	0.5	0.85	10	75	10	0.15	<1	10	35	41	3.24	<10	0.25	406	4	<0.01	27	1690	40	<5	<20	4	0.04	<10	47	<10	3	132
59	L20500N 4950E	15	0.6	1.17	15	145	10	0.17	<1	14	31	31	3.25	<10	0.29	973	3	<0.01	26	990	42	<5	<20	6	0.05	<10	48	<10	10	145
60	L20500N 4975E	35	0.2	1.56	20	105	15	0.32	<1	20	50	38	3.41	<10	0.72	498	4	<0.01	45	840	30	<5	<20	16	0.09	<10	38	<10	18	100
61	L20500N 5025E	5	0.6	1.38	10	70	<5	0.08	<1	4	11	13	1.61	<10	0.06	151	2	<0.01	10	660	26	<5	<20	5	0.03	<10	18	<10	3	35
62	L20500N 5050E	15	0.2	1.22	50	125	10	0.13	<1	19	43	26	5.13	<10	0.41	370	3	<0.01	53	640	30	<5	<20	8	0.08	<10	48	<10	<1	115
63	L20500N 5075E	35	0.3	1.42	15	145	5	0.18	<1	16	37	17	3.00	<10	0.37	569	2	<0.01	26	530	28	<5	<20	5	0.09	<10	35	<10	7	77
64	L20500N 5100E	25	0.4	1.28	40	85	5	0.10	<1	11	26	12	3.46	<10	0.13	599	3	<0.01	22	980	44	<5	<20	2	0.04	<10	38	<10	<1	71
65	L20500N 5125E	10	0.6	0.56	20	115	5	0.26	<1	8	24	14	2.80	<10	0.14	740	2	<0.01	22	1110	30	<5	<20	8	0.06	<10	39	<10	<1	80

Et #	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
66	L20500N 5150E	10	1.7	1.16	10	75	5	0.12	<1	12	27	10	3.05	<10	0.20	744	3	<0.01	18	900	38	<5	<20	4	0.07	<10	36	<10	<1	58
67	L20500N 5175E	5	0.5	0.99	<5	65	<5	0.12	<1	9	24	8	2.22	<10	0.18	860	1	<0.01	13	540	26	<5	<20	2	0.07	<10	30	<10	<1	40
68	L20500N 5200E	10	1.2	0.75	15	95	<5	0.19	<1	11	24	12	2.40	<10	0.20	839	2	<0.01	18	890	36	<5	<20	8	0.06	<10	32	<10	<1	67
69	L20500N 5225E	10	0.9	1.25	5	80	5	0.14	<1	10	35	16	3.02	<10	0.19	355	3	<0.01	17	600	32	<5	<20	4	0.08	<10	44	<10	2	52
70	L20500N 5250E	5	0.4	0.66	10	80	5	0.13	9	10	25	11	2.79	<10	0.17	508	3	<0.01	15	1390	26	<5	<20	4	0.08	<10	48	<10	<1	49
71	L20500N 5275E	5	0.6	0.98	15	100	10	0.15	<1	15	31	21	3.89	<10	0.26	708	3	0.01	29	780	20	<5	<20	8	0.10	<10	43	<10	<1	65
72	L20500N 5300E	10	1.8	2.02	35	75	<5	0.05	<1	18	55	42	4.63	<10	0.65	607	3	<0.01	67	680	22	<5	<20	5	0.01	<10	40	<10	<1	109
73	L20500N 5325E	15	0.8	1.49	15	95	5	0.11	<1	14	40	24	3.86	<10	0.33	438	2	0.01	28	710	18	<5	<20	4	0.12	<10	45	<10	<1	59
74	L20500N 5350E	30	0.7	0.87	10	50	5	0.03	<1	7	14	10	2.40	<10	0.07	391	2	0.01	8	900	20	<5	<20	3	0.11	<10	28	<10	<1	28
75	L20500N 5375E	5	0.5	1.45	5	90	10	0.12	<1	13	37	19	3.59	<10	0.31	638	2	0.01	21	990	18	<5	<20	6	0.12	<10	46	<10	<1	49
76	L20500N 5400E	5	0.5	0.63	10	70	<5	0.06	<1	10	22	15	2.55	<10	0.11	961	2	0.01	16	530	22	<5	<20	6	0.04	<10	38	<10	<1	38
77	L20500N 5425E	15	1.9	1.24	20	90	5	0.08	<1	18	25	21	3.23	<10	0.18	1776	2	0.01	22	1250	22	<5	<20	5	0.06	<10	30	<10	<1	67
78	L20500N 5450E	15	0.8	0.87	10	75	<5	0.07	<1	10	24	20	3.00	<10	0.14	445	2	0.01	18	490	20	<5	<20	6	0.10	<10	43	<10	<1	49
79	L20500N 5475E	15	3.1	1.66	10	100	<5	0.51	<1	17	35	70	2.72	<10	0.43	1666	1	0.02	57	900	18	<5	<20	44	0.05	<10	29	<10	31	64
80	L20500N 5500E	15	3.7	1.73	20	195	<5	1.02	<1	17	49	92	2.76	<10	0.50	1318	1	0.02	77	1090	24	<5	<20	94	0.03	<10	29	<10	68	73

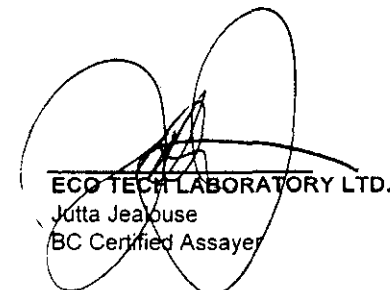
QC DATA:

Repeat:

1	L20400N 4500E	10	<0.2	0.61	15	90	<5	0.13	<1	8	11	9	2.11	<10	0.14	493	2	<0.01	15	390	12	<5	<20	5	0.04	<10	34	<10	<1	33
10	L20400N 4725E	<5	0.7	2.22	10	130	<5	1.40	1	11	32	46	2.11	<10	0.38	978	2	0.02	19	870	34	<5	<20	60	0.03	<10	31	<10	33	101
19	L20400N 4950E	15	0.6	0.85	15	200	5	0.27	<1	14	28	23	3.21	<10	0.26	969	3	<0.01	23	790	30	<5	<20	16	0.06	<10	36	<10	<1	89
21	L20400N 5025E	395	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-
23	L20400N 5075E	20	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-
24	L20400N 5100E	450	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-
25	L20400N 5125E	55	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-
26	L20400N 5150E	30	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-
28	L20400N 5200E	5	0.8	1.15	15	85	<5	0.09	<1	12	29	20	3.16	<10	0.24	727	2	<0.01	22	570	16	<5	<20	3	0.06	<10	44	<10	<1	47
36	L20400N 5400E	10	0.6	0.92	20	50	<5	0.07	<1	11	15	10	2.50	<10	0.08	591	2	<0.01	15	730	16	<5	<20	3	0.04	<10	36	<10	<1	33
45	L20500N 4600E	5	0.2	1.40	<5	65	10	0.13	<1	12	43	16	3.43	<10	0.50	200	2	<0.01	18	290	14	<5	<20	4	0.15	<10	44	<10	5	41
54	L20500N 4825E	20	1.2	1.80	10	345	<5	0.80	2	19	35	40	2.74	<10	0.40	950	1	<0.01	39	740	62	<5	<20	28	0.05	<10	30	<10	33	285
63	L20500N 5075E	35	0.3	1.48	15	145	5	0.18	9	17	40	20	3.24	<10	0.40	637	4	<0.01	32	560	38	<5	<20	5	0.08	<10	38	<10	7	95
71	L20500N 5275E	10	0.7	0.99	20	100	5	0.16	<1	14	30	21	3.93	<10	0.28	655	3	0.01	30	640	20	<5	<20	6	0.08	<10	41	<10	<1	66

Standard:

3EO'04	135	1.6	1.48	50	145	<5	1.39	<1	20	58	86	3.38	<10	0.81	597	<1	0.02	28	690	24	<5	<20	54	0.09	<10	60	<10	11	74
3EO'04	140	1.5	1.48	55	150	<5	1.48	<1	19	60	84	3.49	<10	0.80	623	<1	0.02	31	700	24	<5	<20	53	0.10	<10	60	<10	11	73
3EO'04	140	1.5	1.48	50	145	<5	1.32	<1	19	57	84	3.42	<10	0.80	585	1	0.03	27	660	22	<5	<20	60	0.10	<10	58	<10	10	72


ECO TECH LABORATORY LTD.
 Jutta Jealous
 BC Certified Assayer

ECO TECH LABORATORY LTD.
10041 Dallas Drive
KAMLOOPS, B.C.
V2C 6T4

ICP CERTIFICATE OF ANALYSIS AK 2004-1498

NAVASOTA RESOURCES
#207 141 VICTORIA STREET
KAMLOOPS, BC
V2C 1Z5

Phone: 250-573-5700
Fax : 250-573-4557

No. of samples received: 80
Sample type: Soil
Project #: Not Indicated
Shipment #: Not Indicated

Values in ppm unless otherwise reported

Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
1	L20600N 4500E	<5	0.2	1.60	<5	75	<5	0.13	<1	10	36	28	2.49	<10	0.40	177	<1	<0.01	17	240	12	<5	<20	6	0.21	<10	39	<10	16	41
2	L20600N 4525E	5	0.3	1.48	<5	80	<5	0.13	<1	13	37	26	2.73	<10	0.45	275	1	<0.01	22	230	12	<5	<20	6	0.18	<10	47	<10	12	48
3	L20600N 4550E	<5	0.2	1.25	<5	55	<5	0.08	<1	6	22	23	2.46	<10	0.16	99	1	<0.01	11	300	14	<5	<20	3	0.16	<10	42	<10	6	22
4	L20600N 4575E	200	0.2	0.99	<5	65	<5	0.06	<1	7	21	22	2.74	<10	0.16	118	1	<0.01	9	310	14	<5	<20	4	0.17	<10	46	<10	2	22
5	L20600N 4600E	15	<0.2	1.12	<5	70	<5	0.15	<1	8	28	19	2.84	<10	0.28	234	1	<0.01	13	410	16	<5	<20	8	0.17	<10	54	<10	1	36
6	L20600N 4625E	15	<0.2	1.17	5	85	<5	0.13	<1	10	27	12	3.04	<10	0.34	221	<1	<0.01	14	280	20	<5	<20	6	0.20	<10	55	<10	<1	43
7	L20600N 4650E	<5	0.2	0.98	<5	60	<5	0.09	<1	7	24	15	2.47	<10	0.24	316	2	<0.01	11	360	12	<5	<20	4	0.12	<10	56	<10	<1	33
8	L20600N 4675E	<5	0.3	0.91	<5	130	5	0.14	<1	9	36	10	2.58	<10	0.41	285	1	<0.01	16	340	16	<5	<20	7	0.15	<10	64	<10	<1	42
9	L20600N 4700E	60	0.2	1.18	<5	125	5	0.12	<1	15	39	17	3.29	<10	0.41	735	1	<0.01	19	340	22	<5	<20	6	0.18	<10	66	<10	<1	66
10	L20600N 4725E	20	0.5	1.48	10	110	<5	0.16	<1	15	44	24	3.40	<10	0.51	531	2	<0.01	25	320	20	<5	<20	7	0.21	<10	65	<10	<1	77
11	L20600N 4750E	15	0.8	1.70	10	125	<5	0.16	<1	15	49	30	3.85	<10	0.60	408	2	<0.01	33	400	22	<5	<20	7	0.25	<10	67	<10	<1	83
12	L20600N 4775E	20	1.0	1.09	<5	145	<5	0.13	<1	11	36	16	3.12	<10	0.42	365	1	<0.01	19	390	22	<5	<20	7	0.20	<10	67	<10	<1	62
13	L20600N 4800E	<5	0.8	0.83	<5	110	<5	0.10	<1	8	26	17	3.02	<10	0.24	193	3	<0.01	16	420	22	<5	<20	8	0.15	<10	58	<10	<1	65
14	L20600N 4825E	20	0.5	0.67	5	170	<5	0.11	<1	6	22	12	2.57	<10	0.13	182	2	<0.01	12	390	84	<5	<20	10	0.13	<10	67	<10	<1	52
15	L20600N 4850E	15	0.7	0.19	20	105	<5	0.05	<1	3	7	23	1.56	<10	0.02	59	4	<0.01	16	590	26	<5	<20	15	0.01	<10	29	<10	<1	89
16	L20600N 4875E	20	0.5	0.64	15	120	<5	0.09	<1	16	14	25	3.94	<10	0.13	552	5	<0.01	24	710	38	<5	<20	11	0.05	<10	39	<10	<1	132
17	L20600N 4900E	80	0.4	0.79	20	145	<5	0.07	<1	10	16	27	4.35	<10	0.13	350	5	<0.01	15	890	30	<5	<20	8	0.10	<10	51	<10	<1	96
18	L20600N 4925E	40	0.5	0.31	25	205	<5	0.08	<1	5	7	24	2.57	<10	0.02	179	14	<0.01	21	410	26	<5	<20	9	0.04	<10	41	<10	<1	85
19	L20600N 4950E	30	0.5	0.39	35	215	<5	0.05	<1	16	9	40	4.08	<10	0.03	2485	9	<0.01	22	1400	62	<5	<20	9	0.01	<10	31	<10	<1	137
20	L20600N 4975E	25	0.7	0.91	15	170	<5	0.15	<1	17	21	19	2.51	<10	0.16	3381	2	<0.01	18	710	20	<5	<20	10	0.06	<10	47	<10	<1	87
21	L20600N 5025E	20	0.7	1.50	15	110	<5	0.10	<1	13	30	24	2.86	<10	0.28	717	2	<0.01	27	470	18	<5	<20	7	0.13	<10	49	<10	5	68
22	L20600N 5050E	15	0.6	1.15	15	90	<5	0.15	<1	12	33	16	2.96	<10	0.31	519	2	<0.01	23	410	16	<5	<20	8	0.14	<10	56	<10	<1	58
23	L20600N 5075E	25	0.5	1.05	15	85	<5	0.11	<1	10	23	14	2.80	<10	0.19	731	2	<0.01	17	620	18	<5	<20	5	0.13	<10	45	<10	<1	48
24	L20600N 5100E	25	0.4	1.47	35	75	5	0.09	<1	13	29	21	3.46	<10	0.30	439	3	<0.01	32	810	16	<5	<20	4	0.10	<10	41	<10	<1	62
25	L20600N 5125E	20	0.3	0.89	5	70	<5	0.09	<1	8	21	9	2.53	<10	0.16	654	2	<0.01	13	690	14	<5	<20	3	0.12	<10	53	<10	<1	36

Et #	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
26	L20600N 5150E	15	1.0	1.48	15	85	<5	0.11	<1	10	25	15	2.43	<10	0.25	571	2	<0.01	16	740	14	<5	<20	3	0.11	<10	47	<10	<1	49
27	L20600N 5175E	10	0.6	1.61	30	75	<5	0.10	<1	14	27	21	3.74	<10	0.26	655	3	<0.01	24	810	22	<5	<20	4	0.12	<10	46	<10	<1	62
28	L20600N 5200E	15	0.3	0.74	10	215	<5	0.24	<1	18	29	16	2.87	<10	0.32	4793	<1	<0.01	29	740	18	<5	<20	7	0.21	<10	58	<10	<1	63
29	L20600N 5225E	<5	1.1	0.59	<5	75	<5	0.09	<1	6	21	9	2.11	<10	0.11	463	<1	<0.01	10	580	16	<5	<20	4	0.21	<10	57	<10	<1	34
30	L20600N 5250E	<5	0.5	1.07	15	70	<5	0.11	<1	13	33	22	3.70	<10	0.38	445	2	<0.01	31	1020	16	<5	<20	3	0.15	<10	56	<10	<1	57
31	L20600N 5275E	15	0.9	0.80	5	90	<5	0.13	<1	9	23	11	2.18	<10	0.23	634	<1	<0.01	14	750	16	<5	<20	5	0.16	<10	51	<10	<1	39
32	L20600N 5300E	<5	0.5	1.52	20	165	<5	0.31	<1	18	48	29	3.12	<10	0.74	543	<1	<0.01	43	330	16	<5	<20	16	0.17	<10	52	<10	5	74
33	L20600N 5325E	10	0.7	1.35	15	115	5	0.12	<1	12	37	27	3.42	<10	0.36	236	2	<0.01	33	360	16	<5	<20	7	0.19	<10	50	<10	<1	59
34	L20600N 5350E	10	0.7	0.73	20	130	<5	0.21	<1	9	27	27	2.84	<10	0.24	280	2	<0.01	29	570	18	<5	<20	14	0.08	<10	47	<10	<1	55
35	L20600N 5375E	10	0.4	0.82	15	115	<5	0.08	<1	8	25	28	3.42	<10	0.17	181	2	<0.01	27	690	18	<5	<20	7	0.10	<10	54	<10	<1	52
36	L20600N 5400E	5	0.5	1.40	25	165	<5	0.21	<1	19	42	44	4.18	<10	0.52	408	2	<0.01	56	380	16	<5	<20	17	0.10	<10	48	<10	1	80
37	L20600N 5425E	5	1.3	1.20	20	270	<5	0.79	<1	17	33	42	3.13	<10	0.49	1141	2	<0.01	58	1160	16	<5	<20	72	0.03	<10	36	<10	17	81
38	L20600N 5450E	5	1.0	1.26	20	280	<5	0.74	<1	17	34	46	3.15	<10	0.47	1482	2	<0.01	61	1280	16	<5	<20	68	0.04	<10	38	<10	11	96
39	L20600N 5475E	5	0.9	1.16	15	195	<5	0.51	<1	18	33	44	2.87	<10	0.35	1359	1	<0.01	46	900	16	<5	<20	47	0.06	<10	47	<10	10	78
40	L20600N 5500E	5	1.1	1.27	5	120	<5	0.29	<1	15	35	42	2.88	<10	0.32	598	1	<0.01	40	590	16	<5	<20	26	0.12	<10	55	<10	14	59
41	L20700N 4500E	5	0.2	1.58	<5	75	5	0.12	<1	12	38	27	2.85	<10	0.48	307	1	<0.01	20	360	26	<5	<20	6	0.22	<10	53	<10	14	45
42	L20700N 4525E	10	<0.2	1.71	<5	80	<5	0.15	<1	16	56	31	3.33	<10	0.85	388	<1	<0.01	27	290	16	<5	<20	5	0.31	<10	57	<10	8	52
43	L20700N 4550E	15	<0.2	2.53	15	85	<5	0.14	<1	15	47	25	3.43	<10	0.63	329	<1	<0.01	23	370	24	<5	<20	6	0.25	<10	51	<10	9	62
44	L20700N 4575E	10	<0.2	1.31	<5	55	<5	0.07	<1	9	24	13	2.95	<10	0.27	223	1	<0.01	11	460	24	<5	<20	3	0.20	<10	55	<10	4	31
45	L20700N 4600E	<5	<0.2	2.41	10	85	<5	0.20	<1	20	42	41	4.23	<10	1.05	423	2	<0.01	25	250	22	<5	<20	6	0.18	<10	80	<10	8	56
46	L20700N 4625E	10	<0.2	2.21	5	80	<5	0.20	<1	19	39	37	3.92	<10	0.97	424	<1	<0.01	23	260	20	<5	<20	6	0.18	<10	76	<10	8	53
47	L20700N 4650E	5	<0.2	1.06	5	80	<5	0.12	<1	11	30	14	2.99	<10	0.38	175	<1	<0.01	14	220	18	<5	<20	4	0.21	<10	64	<10	2	35
48	L20700N 4675E	5	<0.2	0.45	<5	95	<5	0.16	<1	5	14	8	1.47	<10	0.13	204	<1	<0.01	5	270	12	<5	<20	8	0.12	<10	51	<10	1	23
49	L20700N 4700E	10	<0.2	0.52	<5	135	<5	0.29	<1	5	16	10	1.82	<10	0.17	1511	<1	<0.01	7	510	16	<5	<20	11	0.14	<10	43	<10	<1	39
50	L20700N 4725E	5	<0.2	0.97	<5	70	10	0.12	<1	12	32	12	2.98	<10	0.32	529	1	<0.01	13	310	14	<5	<20	4	0.22	<10	70	<10	<1	40
51	L20700N 4750E	10	<0.2	1.02	<5	110	5	0.12	<1	10	31	14	3.02	<10	0.35	422	2	<0.01	12	290	14	<5	<20	7	0.16	<10	70	<10	<1	45
52	L20700N 4775E	15	1.1	1.48	15	95	10	0.12	<1	12	36	24	3.31	<10	0.45	395	4	<0.01	21	580	26	<5	<20	7	0.14	<10	56	<10	3	70
53	L20700N 4800E	10	1.0	1.16	5	90	<5	0.08	<1	10	25	23	2.56	<10	0.24	376	3	<0.01	17	440	28	<5	<20	7	0.08	<10	51	<10	5	67
54	L20700N 4825E	5	0.2	1.31	15	95	<5	0.09	<1	10	29	22	3.29	<10	0.32	308	1	<0.01	18	380	26	<5	<20	10	0.13	<10	40	<10	<1	82
55	L20700N 4850E	5	1.1	0.99	15	170	<5	0.07	<1	5	13	18	2.32	<10	0.09	147	3	<0.01	14	390	56	<5	<20	16	0.03	<10	30	<10	3	92
56	L20700N 4875E	5	0.6	0.58	20	170	<5	0.14	<1	8	16	22	2.65	<10	0.13	455	3	<0.01	21	820	32	<5	<20	18	0.03	<10	43	<10	<1	92
57	L20700N 4900E	<5	<0.2	0.52	15	170	<5	0.11	<1	9	15	19	3.30	<10	0.10	323	4	<0.01	15	610	24	<5	<20	12	0.05	<10	47	<10	<1	81
58	L20700N 4925E	50	0.2	0.61	40	120	<5	0.14	<1	10	18	31	3.15	<10	0.14	485	6	<0.01	25	950	22	<5	<20	10	0.04	<10	40	<10	<1	114
59	L20700N 4950E	25	0.3	0.92	20	395	<5	0.37	<1	18	28	27	2.92	<10	0.26	3516	2	<0.01	24	690	26	<5	<20	31	0.05	<10	43	<10	2	132
60	L20700N 4975E	30	0.2	0.63	30	255	<5	0.31	<1	13	13	19	2.65	<10	0.11	3332	2	<0.01	18	980	36	<5	<20	23	0.02	<10	35	<10	<1	120
61	L20700N 5025E	20	0.2	1.02	20	60	<5	0.08	<1	9	25	14	3.06	<10	0.19	410	2	<0.01	17	490	18	<5	<20	4	0.07	<10	53	<10	<1	42
62	L20700N 5050E	15	0.3	0.81	15	85	<5	0.10	<1	8	23	15	2.62	<10	0.18	245	2	<0.01	15	500	16	<5	<20	5	0.08	<10	50	<10	<1	43
63	L20700N 5075E	40	0.2	1.24	30	65	5	0.09	<1	9	28	21	3.25	<10	0.26	268	3	<0.01	20	660	18	<5	<20	4	0.08	<10	43	<10	<1	50
64	L20700N 5100E	40	0.2	1.25	40	115	<5	0.16	<1	13	27	24	3.04	<10	0.27	565	2	<0.01	25	680	20	<5	<20	8	0.07	<10	41	<10	<1	66
65	L20700N 5125E	20	0.2	1.49	15	80	5	0.17	<1	15	44	29	3.50	<10	0.53	463	2	<0.01	31	610	18	<5	<20	4	0.12	<10	51	<10	3	70

Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
66	L20700N 5150E	50	0.5	0.93	5	105	5	0.15	<1	8	24	20	2.42	<10	0.23	1354	1	<0.01	16	670	14	<5	<20	5	0.10	<10	36	<10	<1	51
67	L20700N 5175E	20	0.5	1.05	5	75	<5	0.12	<1	9	27	14	2.74	<10	0.24	301	1	<0.01	15	590	14	<5	<20	6	0.15	<10	45	<10	<1	41
68	L20700N 5200E	20	1.1	1.69	20	150	<5	0.35	<1	21	59	37	3.47	<10	0.93	552	1	<0.01	75	300	16	<5	<20	16	0.12	<10	42	<10	15	89
69	L20700N 5225E	15	0.4	1.58	20	130	<5	0.14	<1	15	47	36	3.84	<10	0.55	326	2	<0.01	41	590	18	<5	<20	5	0.10	<10	47	<10	<1	78
70	L20700N 5250E	15	0.6	1.90	15	115	5	0.15	<1	22	52	36	3.88	<10	0.62	490	2	<0.01	42	730	16	<5	<20	5	0.10	<10	48	<10	10	81
71	L20700N 5275E	<5	0.8	0.59	5	70	<5	0.16	<1	7	20	12	2.07	<10	0.19	355	1	<0.01	13	750	20	<5	<20	7	0.08	<10	38	<10	2	42
72	L20700N 5300E	10	0.4	1.52	20	110	5	0.16	<1	14	41	26	3.64	<10	0.46	353	2	<0.01	33	590	16	<5	<20	5	0.11	<10	44	<10	<1	73
73	L20700N 5325E	5	0.5	1.28	20	130	<5	0.09	<1	13	27	30	3.13	<10	0.26	673	2	<0.01	32	640	16	<5	<20	4	0.03	<10	37	<10	<1	78
74	L20700N 5350E	10	0.7	1.03	15	195	<5	0.20	<1	13	33	37	3.13	<10	0.28	328	2	<0.01	45	600	16	<5	<20	16	0.05	<10	39	<10	3	71
75	L20700N 5375E	5	0.9	1.71	25	280	<5	0.41	4	20	49	54	3.72	<10	0.61	764	3	<0.01	84	750	20	<5	<20	35	0.03	<10	41	<10	11	114
76	L20700N 5400E	10	1.1	1.58	20	215	<5	0.61	<1	18	35	48	2.94	<10	0.44	1449	2	0.01	65	1880	16	<5	<20	57	0.02	<10	37	<10	19	113
77	L20700N 5425E	<5	1.4	1.75	20	200	<5	0.64	<1	15	39	56	2.93	<10	0.41	926	2	0.02	73	1500	18	<5	<20	60	0.02	<10	36	<10	33	79
78	L20700N 5450E	5	1.8	1.94	15	225	<5	0.66	<1	21	49	62	3.22	<10	0.58	1484	2	0.02	73	1120	20	<5	<20	58	0.04	<10	44	<10	22	97
79	L20700N 5475E	5	1.7	1.76	10	195	<5	0.68	<1	17	45	54	3.10	<10	0.50	696	2	0.01	67	930	18	<5	<20	60	0.05	<10	40	<10	21	89
80	L20700N 5500E	5	1.4	1.27	10	170	<5	1.07	<1	7	25	25	1.54	<10	0.47	368	1	0.01	36	1130	14	<5	<20	91	0.02	<10	22	<10	25	47

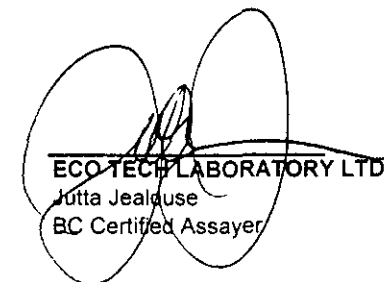
QC DATA:

Repeat:

1	L20600N 4500E	<5	0.2	1.59	<5	70	<5	0.12	<1	11	36	27	2.51	<10	0.40	186	<1	<0.01	18	240	12	<5	<20	4	0.20	<10	40	<10	16	42
10	L20600N 4725E	10	0.5	1.51	5	120	5	0.16	<1	15	45	25	3.48	<10	0.50	555	2	<0.01	28	330	20	<5	<20	7	0.27	<10	69	<10	<1	80
19	L20600N 4950E	30	0.6	0.42	35	210	<5	0.06	<1	17	9	41	4.06	<10	0.03	2578	9	<0.01	22	1480	64	<5	<20	10	0.02	<10	30	<10	<1	137
28	L20600N 5200E	5	0.3	0.77	10	200	<5	0.22	<1	16	30	14	2.64	<10	0.33	3594	<1	<0.01	27	710	16	<5	<20	6	0.19	<10	54	<10	<1	56
36	L20600N 5400E	5	0.4	1.42	25	175	<5	0.20	<1	19	41	44	4.32	<10	0.49	392	2	<0.01	57	420	16	<5	<20	17	0.07	<10	48	<10	<1	79
45	L20700N 4600E	5	<0.2	2.39	<5	80	10	0.19	<1	20	41	41	4.20	<10	1.02	421	3	<0.01	26	250	22	<5	<20	6	0.16	<10	79	<10	9	56
54	L20700N 4825E	5	0.3	1.25	10	85	5	0.08	<1	9	29	21	3.10	<10	0.28	287	2	<0.01	17	380	26	<5	<20	8	0.10	<10	40	<10	<1	76
63	L20700N 5075E	55	0.3	1.25	25	65	<5	0.09	<1	9	27	20	3.21	<10	0.26	244	3	<0.01	20	660	18	<5	<20	4	0.08	<10	42	<10	<1	48
71	L20700N 5275E	<5	0.9	0.59	10	70	<5	0.17	<1	8	20	12	2.07	<10	0.20	407	1	<0.01	15	750	18	<5	<20	6	0.08	<10	38	<10	1	42
80	L20700N 5500E	-	1.5	1.26	10	185	<5	1.18	<1	7	25	25	1.48	<10	0.45	391	1	0.01	36	1160	14	<5	<20	103	0.02	<10	22	<10	28	45

Standard:

3EO'04	140	1.6	1.49	50	140	<5	1.30	<1	16	57	86	3.03	<10	0.82	587	<1	0.02	28	640	22	<5	<20	52	0.12	<10	60	<10	11	74
3EO'04	140	1.4	1.52	60	140	<5	1.32	<1	16	57	88	3.08	<10	0.84	575	<1	0.02	28	660	24	<5	<20	54	0.11	<10	61	<10	11	74
3EO'04	140	1.5	1.52	50	140	<5	1.29	<1	16	56	86	3.02	<10	0.83	557	<1	0.02	28	640	24	<5	<20	53	0.11	<10	60	<10	11	75



ECO TECH LABORATORY LTD.
10041 Dallas Drive
KAMLOOPS, B.C.
V2C 6T4

ICP CERTIFICATE OF ANALYSIS AK 2004-1499

NAVASOTA RESOURCES
#207 141 VICTORIA STREET
KAMLOOPS, BC
V2C 1Z5

Phone: 250-573-5700

Fax : 250-573-4557

No. of samples received: 40

Sample type: Soil

Project #: Not Indicated

Shipment #: Not Indicated

Values in ppm unless otherwise reported

Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bl	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
1	L20800N 4500E	5	0.2	1.16	<5	105	5	0.16	<1	12	32	20	3.39	<10	0.42	600	2	<0.01	16	520	54	<5	<20	10	0.13	<10	43	<10	2	62
2	L20800N 4525E	10	<0.2	2.37	10	105	5	0.17	<1	18	47	36	3.50	<10	0.76	638	2	<0.01	27	520	24	<5	<20	7	0.15	<10	39	<10	14	72
3	L20800N 4550E	<5	0.3	1.39	<5	65	<5	0.10	<1	7	19	14	2.29	<10	0.19	140	2	<0.01	11	360	14	<5	<20	5	0.09	<10	29	<10	13	30
4	L20800N 4575E	15	0.3	2.16	10	100	<5	0.20	<1	14	35	30	2.43	<10	0.46	754	2	0.01	20	460	14	<5	<20	7	0.09	<10	35	<10	30	50
5	L20800N 4600E	<5	0.3	1.84	10	80	<5	0.15	<1	19	26	27	2.42	<10	0.37	1192	2	<0.01	14	470	14	<5	<20	7	0.09	<10	42	<10	23	49
6	L20800N 4625E	10	0.2	2.19	10	90	10	0.29	<1	19	50	38	3.67	<10	1.02	399	1	<0.01	34	280	14	<5	<20	5	0.16	<10	47	<10	15	55
7	L20800N 4650E	5	<0.2	2.24	5	110	<5	0.35	<1	17	28	30	2.41	<10	0.46	3708	2	0.01	22	700	16	<5	<20	11	0.06	<10	42	<10	29	76
8	L20800N 4675E	5	<0.2	0.94	<5	120	5	0.11	<1	10	25	13	2.62	<10	0.29	378	2	<0.01	13	380	14	<5	<20	6	0.13	<10	54	<10	6	33
9	L20800N 4700E	10	<0.2	1.40	10	115	10	0.31	<1	15	44	15	3.78	<10	0.47	615	3	<0.01	23	640	28	<5	<20	12	0.13	<10	49	<10	6	65
10	L20800N 4725E	10	0.3	0.86	<5	50	5	0.11	<1	8	21	11	2.13	<10	0.22	266	1	<0.01	10	320	30	<5	<20	5	0.11	<10	36	<10	5	28
11	L20800N 4750E	30	0.4	0.89	<5	140	<5	0.03	<1	10	11	20	2.10	<10	0.07	400	2	<0.01	14	590	58	<5	<20	3	0.03	<10	32	<10	5	53
12	L20800N 4775E	40	0.9	0.97	25	150	<5	0.09	<1	11	25	22	2.95	<10	0.27	494	3	<0.01	20	630	38	<5	<20	14	0.05	<10	44	<10	1	78
13	L20800N 4800E	5	0.6	0.49	10	310	<5	0.13	<1	27	8	30	2.66	<10	0.07	1591	4	<0.01	22	1250	28	<5	<20	29	<0.01	<10	28	<10	<1	105
14	L20800N 4825E	10	0.4	0.95	15	195	5	0.21	<1	16	33	28	3.15	<10	0.40	1139	3	<0.01	24	900	34	<5	<20	18	0.07	<10	46	<10	<1	118
15	L20800N 4850E	10	0.4	0.70	15	160	<5	0.10	<1	14	23	29	3.05	<10	0.17	1085	4	<0.01	27	1060	18	<5	<20	11	0.04	<10	45	<10	<1	110
16	L20800N 4875E	15	0.4	1.07	10	145	<5	0.15	<1	17	26	23	3.54	<10	0.27	1244	4	<0.01	21	800	24	<5	<20	10	0.06	<10	46	<10	<1	107
17	L20800N 4900E	90	0.5	1.11	20	175	<5	0.21	<1	15	23	29	3.11	<10	0.27	1222	3	<0.01	19	750	52	<5	<20	16	0.06	<10	36	<10	8	122
18	L20800N 4925E	210	0.5	1.26	60	165	<5	0.27	<1	24	30	54	4.12	<10	0.38	1577	4	<0.01	45	1000	38	<5	<20	25	0.04	<10	36	<10	16	202
19	L20800N 4950E	110	0.6	1.36	50	135	5	0.17	<1	19	34	26	4.13	<10	0.30	1106	4	<0.01	31	1010	64	<5	<20	9	0.07	<10	43	<10	<1	154
20	L20800N 4975E	75	0.5	0.83	35	125	5	0.13	<1	13	28	19	3.06	<10	0.23	915	3	<0.01	21	760	30	<5	<20	7	0.06	<10	48	<10	<1	61
21	L20900N 4500E	10	0.2	1.64	35	110	10	0.14	<1	14	42	38	3.92	<10	0.61	405	3	<0.01	20	290	14	<5	<20	6	0.14	<10	45	<10	3	54
22	L20900N 4525E	<5	<0.2	0.99	<5	85	5	0.10	<1	10	18	13	3.28	<10	0.28	436	3	<0.01	9	460	16	<5	<20	6	0.11	<10	36	<10	4	46
23	L20900N 4550E	160	0.2	1.29	10	80	10	0.20	<1	14	43	17	3.48	<10	0.61	409	1	<0.01	18	440	42	<5	<20	7	0.17	<10	53	<10	6	55
24	L20900N 4575E	5	0.2	1.95	5	95	5	0.16	<1	16	41	25	3.55	<10	0.59	533	2	<0.01	22	340	24	<5	<20	5	0.13	<10	50	<10	20	54
25	L20900N 4600E	10	0.2	0.86	<5	70	<5	0.07	<1	9	12	15	2.05	<10	0.13	463	2	0.01	7	410	14	<5	<20	5	0.07	<10	44	<10	9	29

Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
26	L20900N 4625E	<5	0.4	0.76	<5	70	<5	0.09	<1	9	10	23	1.52	<10	0.14	304	1	<0.01	8	470	14	<5	<20	5	0.06	<10	39	<10	6	23
27	L20900N 4650E	<5	0.4	2.19	10	120	<5	0.83	<1	12	17	14	1.98	<10	0.25	929	1	0.02	12	580	18	<5	<20	17	0.08	<10	28	<10	19	69
28	L20900N 4675E	5	0.2	0.81	<5	100	<5	0.24	<1	8	36	11	1.82	<10	0.20	782	1	<0.01	12	490	14	<5	<20	8	0.05	<10	29	<10	3	47
29	L20900N 4700E	5	0.3	2.10	5	80	<5	0.41	<1	9	17	21	1.77	<10	0.22	1599	2	0.01	12	660	16	<5	<20	12	0.05	<10	31	<10	31	47
30	L20900N 4725E	5	0.4	1.61	10	95	10	0.10	<1	12	25	19	3.80	<10	0.20	405	4	<0.01	20	710	30	<5	<20	6	0.10	<10	32	<10	<1	117
31	L20900N 4750E	20	1.2	0.45	25	140	<5	0.12	<1	8	15	35	2.20	<10	0.10	653	3	<0.01	19	760	52	<5	<20	19	0.04	<10	38	<10	<1	79
32	L20900N 4775E	10	1.4	0.71	40	205	<5	0.36	<1	10	7	27	2.50	<10	0.06	379	5	<0.01	26	1290	34	<5	<20	31	<0.01	<10	20	<10	6	153
33	L20900N 4800E	10	0.7	0.36	15	180	<5	0.09	<1	4	15	17	1.84	<10	0.05	165	5	<0.01	15	700	34	<5	<20	13	0.03	<10	34	<10	<1	85
34	L20900N 4825E	10	0.5	0.96	15	180	<5	0.21	<1	14	31	31	3.06	<10	0.34	953	4	<0.01	22	670	34	<5	<20	12	0.07	<10	52	<10	5	106
35	L20900N 4850E	5	0.5	1.01	20	135	<5	0.23	<1	11	33	41	3.48	<10	0.26	495	4	<0.01	23	890	24	<5	<20	11	0.10	<10	57	<10	2	99
36	L20900N 4875E	5	0.5	1.20	50	140	<5	0.63	<1	11	28	46	2.55	<10	0.23	1378	3	<0.01	28	1390	30	<5	<20	27	0.02	<10	42	<10	18	179
37	L20900N 4900E	35	0.5	1.08	40	135	<5	0.63	<1	11	24	41	2.79	<10	0.21	810	3	<0.01	23	1060	30	<5	<20	26	0.03	<10	45	<10	10	131
38	L20900N 4925E	30	0.7	1.50	45	165	<5	0.78	<1	16	31	50	3.24	<10	0.35	1088	3	<0.01	32	890	30	<5	<20	32	0.04	<10	44	<10	25	163
39	L20900N 4950E	5	0.4	0.77	25	175	<5	0.22	<1	8	21	27	2.97	<10	0.18	276	4	<0.01	20	500	32	<5	<20	16	0.05	<10	42	<10	<1	109
40	L20900N 4975E	40	0.5	1.11	65	125	<5	0.11	<1	16	27	33	4.15	<10	0.32	501	4	<0.01	35	620	26	<5	<20	7	0.04	<10	41	<10	<1	94

QC DATA:

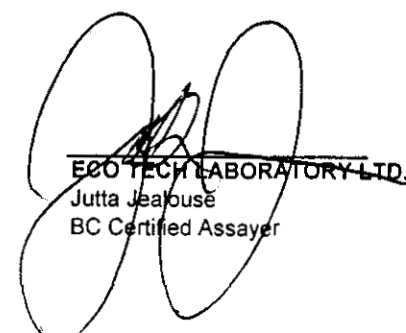
Repeat:

1	L20800N 4500E	5	<0.2	1.14	<5	90	10	0.14	<1	12	32	19	3.36	<10	0.43	586	3	<0.01	17	500	52	<5	<20	9	0.11	<10	45	<10	3	61
10	L20800N 4725E	10	0.4	0.83	<5	50	5	0.10	<1	8	20	11	2.10	<10	0.21	270	1	<0.01	9	330	30	<5	<20	5	0.11	<10	36	<10	4	29
19	L20800N 4950E	140	0.6	1.32	40	125	5	0.15	<1	17	31	28	3.98	<10	0.29	1112	3	<0.01	28	930	58	<5	<20	8	0.06	<10	43	<10	<1	140
28	L20900N 4675E	5	0.5	0.77	<5	100	<5	0.24	<1	8	35	11	1.83	<10	0.19	843	1	<0.01	12	480	16	<5	<20	8	0.05	<10	29	<10	4	47
36	L20900N 4875E	10	0.5	1.17	50	135	<5	0.62	<1	11	25	42	2.43	<10	0.20	1396	3	<0.01	26	1410	30	<5	<20	26	0.02	<10	41	<10	18	170

Standard:

GEO'04	140	1.4	1.52	55	145	<5	1.29	<1	16	58	86	3.03	<10	0.82	556	<1	0.02	28	640	20	<5	<20	53	0.10	<10	61	<10	11	73
GEO'04	140	1.6	1.49	55	145	<5	1.27	<1	16	56	88	3.01	<10	0.82	566	<1	0.02	28	650	22	<5	<20	54	0.11	<10	60	<10	12	74

JJ/jm/sc
11/1498
KLS/04


ECO TECH LABORATORY LTD.
 Jutta Jealous
 BC Certified Assayer

ECO TECH LABORATORY LTD.
10041 Dallas Drive
KAMLOOPS, B.C.
V2C 6T4

ICP CERTIFICATE OF ANALYSIS AK 2004-1500

NAVASOTA RESOURCES
#207 141 VICTORIA STREET
KAMLOOPS, BC
V2C 1Z5

Phone: 250-573-5700

Fax : 250-573-4557

No. of samples received: 80

Sample type: Soil

Project #: None Given

Shipment #: None Given

Samples submitted by: Not Indicated

Values in ppm unless otherwise reported

Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
1	L21000N 4500E	5	0.3	1.11	<5	110	5	0.12	<1	11	30	16	2.62	<10	0.34	461	1	0.01	15	360	16	<5	<20	5	0.16	<10	47	<10	11	44
2	L21000N 4525E	5	<0.2	1.02	<5	155	5	0.24	<1	9	34	14	2.25	<10	0.44	341	1	0.01	16	280	16	<5	<20	9	0.15	<10	37	<10	12	46
3	L21000N 4550E	15	<0.2	1.54	<5	145	5	0.20	<1	17	43	27	3.28	<10	0.58	999	1	0.01	22	300	16	<5	<20	6	0.19	<10	48	<10	26	51
4	L21000N 4575E	25	<0.2	1.05	<5	65	5	0.07	<1	7	18	13	3.00	<10	0.23	247	3	0.01	10	470	18	<5	<20	3	0.09	<10	36	<10	3	32
5	L21000N 4600E	130	0.2	0.90	<5	70	<5	0.14	<1	11	10	11	2.51	<10	0.15	610	2	0.01	6	330	50	<5	<20	7	0.08	<10	50	<10	7	42
6	L21000N 4625E	75	0.2	0.84	<5	70	<5	0.15	<1	9	11	11	2.40	<10	0.15	512	2	0.01	6	310	52	<5	<20	6	0.07	<10	49	<10	4	40
7	L21000N 4650E	20	0.2	0.47	<5	40	<5	0.07	<1	5	6	19	1.52	<10	0.07	166	<1	0.01	5	330	12	<5	<20	3	0.07	<10	55	<10	3	21
8	L21000N 4675E	10	<0.2	1.96	<5	80	10	0.20	<1	19	50	22	3.98	<10	0.99	480	1	0.01	28	410	16	<5	<20	5	0.15	<10	41	<10	13	67
9	L21000N 4700E	10	0.2	1.35	<5	60	<5	0.13	<1	10	24	12	2.23	<10	0.22	411	1	0.02	13	330	16	<5	<20	6	0.09	<10	36	<10	10	43
10	L21000N 4725E	10	0.5	1.92	45	135	<5	1.29	<1	13	71	107	2.08	<10	0.40	1968	<1	0.02	19	670	12	<5	<20	24	0.07	<10	57	<10	103	47
11	L21000N 4750E	15	0.7	2.20	40	110	<5	1.53	<1	8	30	72	1.92	<10	0.13	451	1	0.02	17	630	16	<5	<20	38	0.06	<10	24	<10	43	50
12	L21000N 4775E	<5	0.6	0.79	20	155	<5	2.01	1	4	13	26	1.00	<10	0.07	281	<1	0.01	9	860	10	<5	<20	72	0.02	<10	14	<10	17	109
13	L21000N 4800E	<5	1.1	2.33	65	140	<5	1.22	4	12	24	56	2.38	10	0.13	687	2	0.02	27	860	32	<5	<20	44	0.05	<10	26	<10	37	500
14	L21000N 4825E	15	1.0	1.35	45	165	<5	1.76	4	11	23	57	2.25	<10	0.23	242	1	0.02	22	1060	44	<5	<20	66	0.03	<10	37	<10	25	322
15	L21000N 4850E	10	1.0	1.15	20	125	<5	0.25	4	16	30	50	2.92	<10	0.27	971	2	0.01	32	1070	34	<5	<20	18	0.05	<10	41	<10	17	190
16	L21000N 4875E	5	0.6	1.34	10	155	<5	0.17	1	15	40	50	3.62	<10	0.33	667	3	0.01	29	700	24	<5	<20	9	0.12	<10	55	<10	10	135
17	L21000N 4900E	25	0.6	0.62	20	125	<5	0.19	<1	7	13	20	2.11	<10	0.10	363	2	0.01	12	420	26	<5	<20	14	0.07	<10	32	<10	5	55
18	L21000N 4925E	5	0.3	1.21	<5	110	5	0.26	<1	11	41	18	2.76	<10	0.48	507	<1	0.01	20	580	18	<5	<20	6	0.14	<10	47	<10	9	62
19	L21000N 4950E	20	0.2	2.37	15	155	<5	0.19	<1	20	42	32	3.07	<10	0.51	559	1	0.01	30	640	28	<5	<20	6	0.13	<10	34	<10	18	95
20	L21000N 4975E	20	0.4	1.13	5	115	10	0.20	<1	13	36	18	3.16	<10	0.39	557	2	0.01	20	500	22	<5	<20	5	0.15	<10	45	<10	7	79
21	L21000N 5025E	5	0.4	1.00	5	125	5	0.14	<1	15	27	22	3.18	<10	0.20	910	1	0.01	20	880	22	<5	<20	7	0.11	<10	42	<10	3	73
22	L21000N 5050E	15	0.6	1.21	<5	90	<5	0.21	<1	9	28	18	2.34	<10	0.31	377	1	0.01	18	400	16	<5	<20	10	0.11	<10	35	<10	7	49
23	L21000N 5075E	60	0.2	1.07	<5	100	10	0.15	<1	13	35	17	3.37	<10	0.38	350	1	<0.01	25	390	18	<5	<20	4	0.15	<10	52	<10	7	56
24	L21000N 5100E	10	0.5	1.12	<5	105	10	0.34	<1	10	33	13	2.69	<10	0.33	284	<1	0.01	16	390	14	<5	<20	13	0.17	<10	42	<10	12	42
25	L21000N 5125E	10	0.3	1.46	5	105	5	0.33	<1	16	48	22	2.72	<10	0.69	316	<1	<0.01	31	310	14	<5	<20	7	0.23	<10	31	<10	22	55

N.	OTA	JUR	PCE																		CATI		ANAI		AK	-150	ECC		+LA		TOF		J.	
Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn				
26	L21000N 5150E	15	0.5	1.50	10	165	<5	0.55	<1	20	40	32	2.95	<10	0.56	687	<1	0.01	46	410	18	<5	<20	19	0.12	<10	36	<10	20	82				
27	L21000N 5175E	20	1.3	1.69	15	215	<5	0.53	<1	23	45	71	3.70	<10	0.52	1283	<1	0.02	103	450	28	<5	<20	35	0.12	<10	27	<10	45	114				
28	L21000N 5200E	40	0.5	1.26	10	150	<5	0.19	<1	15	30	31	3.31	<10	0.28	601	1	0.01	34	560	22	<5	<20	8	0.11	<10	37	<10	6	106				
29	L21000N 5225E	15	0.3	1.31	10	140	10	0.21	<1	17	35	20	3.54	<10	0.37	505	1	0.01	28	640	18	<5	<20	7	0.19	<10	40	<10	11	93				
30	L21000N 5250E	20	0.3	0.90	5	100	10	0.10	<1	13	24	20	3.36	<10	0.19	819	1	0.01	19	610	20	<5	<20	3	0.14	<10	38	<10	5	66				
31	L21000N 5275E	20	0.2	1.23	35	120	5	0.19	<1	25	36	42	3.93	<10	0.51	871	2	<0.01	71	570	20	<5	<20	7	0.10	<10	31	<10	6	107				
32	L21000N 5300E	15	2.2	1.31	20	205	<5	1.19	<1	12	31	55	2.17	<10	0.39	1479	<1	0.02	85	1090	16	<5	<20	72	0.05	<10	27	<10	31	66				
33	L21000N 5325E	20	0.5	1.37	20	135	10	0.52	<1	13	33	28	3.76	<10	0.35	322	2	0.01	38	380	16	<5	<20	38	0.14	<10	54	<10	9	56				
34	L21000N 5350E	15	0.2	1.00	15	125	5	0.24	<1	9	23	29	3.84	<10	0.18	183	2	0.01	29	340	22	<5	<20	19	0.06	<10	55	<10	<1	67				
35	L21000N 5375E	<5	0.4	0.70	<5	120	10	0.25	<1	7	26	13	2.43	<10	0.19	242	1	0.01	15	370	14	<5	<20	12	0.16	<10	61	<10	5	37				
36	L21000N 5400E	5	0.4	1.31	<5	110	10	0.14	<1	14	31	22	3.01	<10	0.22	400	1	0.02	20	350	24	<5	<20	6	0.22	<10	44	<10	16	54				
37	L21000N 5425E	10	<0.2	1.97	5	115	5	0.31	<1	23	57	33	3.73	<10	0.77	468	<1	0.01	51	300	28	<5	<20	6	0.24	<10	45	<10	25	80				
38	L21000N 5450E	10	0.5	2.03	<5	135	10	0.24	<1	19	55	26	4.07	<10	0.42	422	1	0.02	22	270	26	<5	<20	5	0.41	<10	49	<10	31	74				
39	L21000N 5475E	<5	0.4	1.52	<5	150	<5	0.39	<1	17	42	41	2.94	<10	0.48	703	<1	0.02	40	350	26	<5	<20	19	0.16	<10	38	<10	33	64				
40	L21000N 5500E	10	0.6	2.20	10	250	5	0.49	<1	20	51	50	3.64	<10	0.63	735	2	0.02	66	600	34	<5	<20	30	0.13	<10	46	<10	31	108				
41	L21100N 4500E	<5	<0.2	1.10	<5	100	5	0.12	<1	9	27	15	2.70	<10	0.30	247	2	0.01	14	360	24	<5	<20	5	0.17	<10	49	<10	12	32				
42	L21100N 4525E	5	<0.2	1.29	<5	115	10	0.18	<1	19	36	23	2.94	<10	0.47	802	1	0.01	19	290	28	<5	<20	5	0.22	<10	50	<10	21	44				
43	L21100N 4550E	5	0.9	2.34	10	145	<5	0.62	<1	12	27	57	2.13	20	0.24	2456	2	0.02	20	1350	28	<5	<20	23	0.03	<10	42	<10	131	46				
44	L21100N 4575E	25	<0.2	1.22	<5	100	5	0.13	<1	11	26	17	3.03	<10	0.27	452	2	0.01	12	260	22	<5	<20	4	0.16	<10	51	<10	20	39				
45	L21100N 4600E	5	0.4	2.77	15	250	5	0.56	<1	21	52	58	4.12	10	0.66	684	1	0.02	45	430	30	<5	<20	21	0.16	<10	52	<10	87	87				
46	L21100N 4625E	20	0.4	2.80	15	255	<5	0.57	<1	22	52	59	4.04	10	0.64	687	2	0.02	46	440	30	<5	<20	22	0.15	<10	49	<10	90	86				
47	L21100N 4650E	15	<0.2	0.80	10	105	5	0.12	<1	10	45	10	2.91	<10	0.17	361	2	0.02	16	270	22	<5	<20	5	0.12	<10	61	<10	3	30				
48	L21100N 4675E	<5	0.3	1.94	15	140	5	0.20	<1	22	34	32	2.95	<10	0.34	1007	2	0.02	16	450	42	<5	<20	7	0.14	<10	49	<10	47	48				
49	L21100N 4700E	5	0.3	1.39	10	125	5	0.99	<1	10	30	24	3.44	<10	0.36	325	2	0.02	13	380	22	<5	<20	25	0.14	<10	53	<10	16	56				
50	L21100N 4725E	5	0.4	0.20	20	50	<5	0.24	<1	4	5	34	1.73	<10	0.02	67	3	<0.01	17	240	22	<5	<20	8	0.03	<10	23	<10	<1	61				
51	L21100N 4750E	35	0.8	1.55	20	170	<5	1.10	<1	16	40	35	3.14	<10	0.42	1298	1	0.02	24	430	68	<5	<20	28	0.11	<10	46	<10	21	108				
52	L21100N 4775E	5	0.9	2.01	30	150	<5	1.53	3	12	25	57	2.36	<10	0.18	1692	1	0.02	25	900	18	<5	<20	38	0.05	<10	41	<10	43	115				
53	L21100N 4800E	15	0.2	2.49	5	145	5	0.58	<1	23	70	44	3.69	<10	0.79	478	1	0.01	44	260	22	<5	<20	15	0.18	<10	54	<10	37	77				
54	L21100N 4825E	5	0.6	0.65	15	215	<5	0.27	<1	7	20	28	2.19	<10	0.15	446	2	0.01	20	450	22	<5	<20	17	0.06	<10	32	<10	2	114				
55	L21100N 4850E	15	0.6	0.88	<5	380	<5	0.68	1	12	55	30	3.20	<10	0.34	1232	2	0.02	24	480	18	<5	<20	29	0.13	<10	58	<10	5	209				
56	L21100N 4875E	5	0.3	0.96	5	135	5	0.30	<1	11	42	44	3.52	<10	0.23	583	3	0.01	26	880	26	<5	<20	13	0.10	<10	65	<10	1	119				
57	L21100N 4900E	<5	1.4	2.04	15	190	<5	1.47	2	13	36	71	2.27	<10	0.39	1300	2	0.02	38	1560	48	<5	<20	55	0.05	<10	35	<10	35	102				
58	L21100N 4925E	5	0.6	1.17	10	155	<5	0.60	<1	10	24	24	2.79	<10	0.20	574	2	0.02	16	490	38	<5	<20	26	0.15	<10	36	<10	15	91				
59	L21100N 4950E	20	0.3	1.06	30	165	5	0.16	<1	17	29	32	3.53	<10	0.24	1079	4	0.01	24	580	40	<5	<20	10	0.11	<10	55	<10	2	105				
60	L21100N 4975E	5	0.4	1.27	<5	135	5	0.27	<1	14	38	21	2.70	<10	0.45	856	1	0.01	20	610	20	<5	<20	11	0.17	<10	47	<10	15	65				
61	L21100N 5025E	5	0.5	1.50	10	180	<5	0.21	<1	18	35	29	3.42	<10	0.38	548	2	0.01	29	530	28	<5	<20	10	0.12	<10	41	<10	13	90				
62	L21100N 5050E	20	0.4	1.20	<5	225	5	0.29	<1	14	36	26	2.89	<10	0.45	754	1	0.01	29	450	24	<5	<20	13	0.15	<10	40	<10	13	77				
63	L21100N 5075E	5	1.0	1.67	10	310	<5	0.56	<1	17	44	49	3.01	<10	0.58	1346	<1	0.01	55	610	42	<5	<20	30	0.10	<10	37	<10	46	119				
64	L21100N 5100E	<5	1.2	1.14	10	235	<5	0.77	1	16	27	59	2.09	<10	0.33	1745	<1	0.01	61	1330	24	<5	<20	53	0.03	<10	30	<10	47	111				
65	L21100N 5125E	15	0.5	0.68	5	210	<5	0.55	<1	9	21	38	1.85	<10	0.18	438	<1	0.01	27	750	22	<5	<20	35	0.08	<10	26	<10	18	70				

N	IOTA	OUR	P CE														ICAT	ANA	AK	1-150	ECC										H LA	ATOI	D.
Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn			
66	L21100N 5150E	15	0.3	0.85	5	80	5	0.15	<1	10	29	26	3.64	<10	0.15	88	2	0.01	18	280	24	<5	<20	9	0.19	<10	55	<10	5	41			
67	L21100N 5175E	5	2.3	1.91	10	205	<5	1.11	<1	12	30	51	2.21	<10	0.29	1439	1	0.02	44	820	18	<5	<20	61	0.08	<10	23	<10	38	45			
68	L21100N 5200E	<5	0.6	1.81	10	135	5	0.22	<1	19	41	28	3.26	<10	0.44	746	2	0.01	27	470	22	<5	<20	8	0.18	<10	41	<10	16	93			
69	L21100N 5225E	<5	0.8	0.81	<5	135	<5	0.22	<1	8	24	13	2.65	<10	0.19	493	1	0.01	18	480	22	<5	<20	11	0.16	<10	39	<10	4	53			
70	L21100N 5250E	15	0.6	0.86	5	190	5	0.25	<1	10	30	16	3.18	<10	0.29	413	1	0.01	23	580	18	<5	<20	12	0.15	<10	48	<10	4	84			
71	L21100N 5275E	10	0.4	1.78	30	130	<5	0.12	<1	18	39	30	3.47	<10	0.40	534	2	0.01	37	520	18	<5	<20	7	0.11	<10	36	<10	12	73			
72	L21100N 5300E	15	<0.2	1.37	25	205	5	0.08	<1	18	39	39	3.58	<10	0.40	344	2	0.01	47	260	22	<5	<20	5	0.08	<10	43	<10	5	86			
73	L21100N 5325E	<5	0.6	0.77	<5	170	10	0.21	<1	13	31	16	3.25	<10	0.28	655	<1	0.01	20	630	18	<5	<20	11	0.18	<10	46	<10	6	55			
74	L21100N 5350E	5	0.3	0.94	<5	145	5	0.20	<1	14	31	18	3.05	<10	0.21	1092	2	0.01	18	490	18	<5	<20	10	0.17	<10	47	<10	7	65			
75	L21100N 5375E	<5	1.0	1.36	<5	285	<5	0.78	<1	24	23	52	1.80	<10	0.23	3671	<1	0.02	34	870	20	<5	<20	45	0.05	<10	40	<10	36	55			
76	L21100N 5400E	<5	0.5	1.62	<5	135	<5	0.18	<1	14	47	60	3.09	<10	0.38	288	<1	0.02	31	420	18	<5	<20	8	0.19	<10	34	<10	39	58			
77	L21100N 5425E	5	0.3	1.64	<5	180	5	0.57	<1	16	59	27	2.76	<10	0.78	527	<1	0.02	28	340	14	<5	<20	14	0.25	<10	34	<10	23	63			
78	L21100N 5450E	<5	1.0	1.70	<5	220	<5	0.52	1	20	43	77	2.37	<10	0.38	1588	1	0.02	39	600	18	<5	<20	34	0.12	<10	45	<10	40	56			
79	L21100N 5475E	20	1.7	2.40	5	235	<5	0.44	<1	16	37	53	2.06	10	0.22	2828	1	0.02	29	1660	20	<5	<20	34	0.03	<10	42	<10	63	47			
80	L21100N 5500E	15	1.4	2.02	<5	305	<5	0.46	<1	18	46	64	2.54	10	0.45	1436	<1	0.02	39	920	22	<5	<20	33	0.10	<10	47	<10	43	85			

QC DATA:

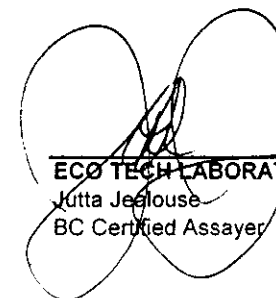
Repeat:

1	L21000N 4500E	<5	0.2	1.08	<5	110	10	0.11	<1	11	30	14	2.61	<10	0.34	498	2	0.01	14	340	16	<5	<20	4	0.13	<10	46	<10	11	44
10	L21000N 4725E	<5	0.5	1.96	45	135	<5	1.31	<1	12	75	116	1.98	<10	0.39	2052	<1	0.02	20	700	12	<5	<20	26	0.07	<10	58	<10	106	47
19	L21000N 4950E	5	0.2	2.29	15	150	5	0.18	<1	20	41	31	3.06	<10	0.51	546	1	0.01	31	600	30	<5	<20	6	0.14	<10	36	<10	15	93
28	L21000N 5200E	20	0.5	1.22	15	150	5	0.18	<1	15	30	27	3.31	<10	0.29	616	1	0.01	34	540	24	<5	<20	9	0.12	<10	39	<10	5	103
36	L21000N 5400E	5	0.5	1.28	<5	115	5	0.15	<1	15	31	22	3.02	<10	0.22	425	1	0.02	20	330	26	<5	<20	6	0.18	<10	41	<10	15	52
45	L21100N 4600E	10	0.4	2.65	15	210	<5	0.52	<1	21	50	55	3.88	<10	0.67	635	2	0.02	43	450	32	<5	<20	21	0.15	<10	46	<10	76	83
54	L21100N 4825E	5	0.6	0.63	15	195	<5	0.26	1	7	21	27	2.21	<10	0.15	444	2	0.01	21	450	20	<5	<20	15	0.07	<10	32	<10	1	113
63	L21100N 5075E	15	0.9	1.65	5	305	<5	0.54	<1	17	43	49	3.09	<10	0.58	1329	1	0.01	53	580	42	<5	<20	29	0.09	<10	37	<10	46	119
71	L21100N 5275E	10	0.5	1.77	35	135	10	0.13	<1	19	38	30	3.58	<10	0.39	599	2	0.01	38	510	18	<5	<20	5	0.11	<10	39	<10	11	77

Standard:

GEO'04	140	1.6	1.52	50	145	<5	1.35	<1	17	59	88	3.16	<10	0.81	582	1	0.03	28	610	20	<5	<20	54	0.10	<10	62	<10	10	74
GEO'04	140	1.5	1.47	50	145	<5	1.30	<1	16	56	88	3.07	<10	0.78	571	<1	0.03	29	610	20	<5	<20	52	0.11	<10	58	<10	10	76
GEO'04	140	1.5	1.46	50	140	<5	1.28	<1	16	56	87	3.03	<10	0.77	568	<1	0.03	29	590	20	<5	<20	54	0.12	<10	59	<10	10	74

JJ/sc
 I#1500/1500a
 <LS/04


ECO TECH LABORATORY LTD.
 Jutta Jeelouse
 BC Certified Assayer

ECO TECH LABORATORY LTD.
10041 Dallas Drive
KAMLOOPS, B.C.
V2C 6T4

ICP CERTIFICATE OF ANALYSIS AK 2004-1501

NAVASOTA RESOURCES
#207 141 VICTORIA STREET
KAMLOOPS, BC
V2C 1Z5

Phone: 250-573-5700

Fax : 250-573-4557

No. of samples received: 40

Sample type: Soil

Project #: None Given

Shipment #: None Given

Samples submitted by: Not Indicated

Values in ppm unless otherwise reported

Et #.	Tag #	Au (ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
1	L21200N 4500E	<5	0.2	1.26	<5	260	<5	0.54	<1	15	33	30	2.83	<10	0.49	751	2	0.02	17	650	30	<5	<20	41	0.10	<10	36	<10	32	64
2	L21200N 4525E	5	0.6	1.81	5	235	5	0.61	<1	16	32	38	2.69	<10	0.40	1191	2	0.02	16	510	20	<5	<20	27	0.14	<10	36	<10	46	78
3	L21200N 4550E	<5	0.5	1.20	<5	130	5	0.32	<1	13	15	19	2.15	<10	0.14	623	2	0.02	8	510	18	<5	<20	14	0.12	<10	35	<10	24	34
4	L21200N 4575E	10	0.2	0.88	<5	200	10	0.15	<1	10	24	13	2.72	<10	0.27	596	1	0.01	12	350	16	<5	<20	8	0.17	<10	39	<10	7	44
5	L21200N 4600E	5	0.4	2.07	15	275	<5	0.57	<1	12	30	26	2.57	<10	0.42	443	1	0.01	21	510	18	<5	<20	28	0.09	<10	29	<10	33	99
6	L21200N 4625E	<5	0.2	0.78	<5	135	10	0.17	<1	8	20	20	2.82	<10	0.20	176	2	0.01	10	380	16	<5	<20	8	0.19	<10	98	<10	9	39
7	L21200N 4650E	<5	0.8	2.44	10	125	<5	0.38	<1	12	41	100	2.35	10	0.31	644	2	0.02	19	600	20	<5	<20	16	0.08	<10	35	<10	77	40
8	L21200N 4675E	<5	0.5	2.02	10	145	<5	1.11	<1	9	30	41	1.79	<10	0.27	1081	2	0.02	15	1380	14	<5	<20	36	0.04	<10	36	<10	51	52
9	L21200N 4700E	10	0.2	1.34	10	80	10	0.24	22	15	62	28	3.50	<10	0.66	281	1	0.01	27	250	18	<5	<20	6	0.28	<10	48	<10	17	47
10	L21200N 4725E	<5	<0.2	0.81	10	85	5	0.14	<1	8	30	13	2.07	<10	0.32	216	1	0.01	14	300	20	<5	<20	7	0.12	<10	34	<10	8	48
11	L21200N 4750E	<5	0.2	1.20	50	110	10	0.13	<1	16	116	33	4.11	<10	0.56	282	3	0.01	47	370	16	<5	<20	7	0.13	<10	82	<10	<1	60
12	L21200N 4775E	<5	0.4	2.01	15	200	5	0.17	<1	14	30	36	2.70	<10	0.19	1596	2	0.02	17	560	20	<5	<20	9	0.08	<10	34	<10	28	80
13	L21200N 4800E	<5	0.2	1.97	15	155	15	0.27	<1	19	61	31	4.86	<10	0.80	418	3	0.01	36	290	22	<5	<20	10	0.18	<10	68	<10	7	110
14	L21200N 4825E	10	0.9	1.20	30	120	<5	0.12	<1	9	16	18	2.70	<10	0.10	443	4	0.02	14	600	52	<5	<20	8	0.07	<10	30	<10	4	79
15	L21200N 4850E	5	0.9	1.45	10	115	5	0.67	2	13	20	31	2.40	<10	0.21	1361	3	0.02	21	590	46	<5	<20	29	0.05	<10	32	<10	14	115
16	L21200N 4875E	5	0.4	0.59	35	170	<5	0.08	<1	8	16	15	2.78	<10	0.08	480	3	0.01	20	290	34	<5	<20	9	0.07	<10	40	<10	<1	83
17	L21200N 4900E	<5	0.5	1.24	20	165	10	0.36	<1	18	38	36	3.16	<10	0.61	508	3	0.01	63	500	22	<5	<20	18	0.07	<10	31	<10	35	165
18	L21200N 4925E	<5	0.7	0.82	20	215	5	0.47	<1	11	20	39	3.03	<10	0.12	458	4	0.01	21	540	42	<5	<20	25	0.07	<10	40	<10	14	94
19	L21200N 4950E	10	<0.2	1.08	30	110	5	0.27	<1	22	39	68	3.26	<10	0.57	754	3	0.01	43	490	26	<5	<20	14	0.12	<10	24	<10	17	88
20	L21200N 4975E	10	0.3	0.82	<5	90	5	0.18	<1	8	20	18	2.19	<10	0.15	331	2	0.01	12	360	18	<5	<20	11	0.12	<10	31	<10	8	41
21	L21300N 4500E	105	<0.2	1.70	30	75	10	0.21	<1	16	33	26	4.58	<10	0.60	556	3	0.01	19	370	50	<5	<20	8	0.16	<10	39	<10	11	176
22	L21300N 4525E	20	<0.2	0.53	<5	60	10	0.14	<1	7	11	10	2.24	<10	0.13	193	2	0.01	5	350	18	<5	<20	7	0.12	<10	45	<10	6	28
23	L21300N 4550E	10	0.3	1.46	10	90	5	0.10	<1	14	15	17	3.39	<10	0.24	1040	3	0.02	7	470	18	<5	<20	6	0.12	<10	37	<10	9	59
24	L21300N 4575E	5	0.7	1.47	<5	155	<5	0.54	7	9	22	38	2.21	<10	0.14	898	2	0.02	11	330	12	<5	<20	27	0.11	<10	26	<10	51	67
25	L21300N 4600E	5	0.5	1.26	<5	145	10	0.61	<1	9	32	25	2.52	<10	0.40	224	1	0.02	16	300	14	<5	<20	26	0.14	<10	24	<10	29	38

N	OTA	JUR	P CI ICAT ANA S AK I-15C																	COT		LAB		ORY						
Et #.	Tag #	Au (ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
26	L21300N 4625E	320	0.3	1.52	<5	150	10	0.38	<1	13	47	21	3.21	<10	0.53	315	2	0.01	20	210	16	<5	<20	16	0.22	<10	34	<10	19	46
27	L21300N 4650E	5	0.2	1.99	<5	80	10	0.23	<1	18	104	22	3.81	<10	0.81	358	2	0.01	31	240	14	<5	<20	6	0.24	<10	34	<10	17	51
28	L21300N 4675E	5	0.4	1.58	<5	90	10	0.16	<1	9	37	14	2.70	<10	0.31	180	1	0.02	13	320	18	<5	<20	7	0.18	<10	37	<10	11	33
29	L21300N 4700E	5	<0.2	0.78	<5	70	5	0.14	<1	6	32	9	1.88	<10	0.22	83	1	0.01	11	260	18	<5	<20	7	0.17	<10	47	<10	9	23
30	L21300N 4725E	5	0.2	1.09	<5	70	10	0.08	<1	10	43	13	2.88	<10	0.34	249	2	0.01	15	250	14	<5	<20	6	0.18	<10	71	<10	6	30
31	L21300N 4750E	<5	0.4	0.77	5	245	5	0.21	<1	8	19	11	2.87	<10	0.18	314	2	0.01	11	250	14	<5	<20	12	0.14	<10	70	<10	4	43
32	L21300N 4775E	5	0.2	0.39	<5	70	5	0.07	<1	5	31	7	1.13	<10	0.10	264	<1	0.01	7	190	12	<5	<20	5	0.10	<10	32	<10	6	23
33	L21300N 4800E	20	0.2	0.99	<5	50	10	0.12	<1	8	34	14	2.71	<10	0.24	160	2	0.02	13	270	12	<5	<20	5	0.17	<10	43	<10	5	29
34	L21300N 4825E	5	0.6	1.56	5	100	5	0.14	<1	12	47	23	3.42	<10	0.30	485	2	0.02	20	290	14	<5	<20	6	0.13	<10	51	<10	5	50
35	L21300N 4850E	10	<0.2	1.83	<5	295	5	0.31	<1	20	63	53	3.16	<10	0.96	582	1	0.01	39	370	14	<5	<20	10	0.20	<10	37	<10	21	57
36	L21300N 4875E	5	2.6	1.01	15	135	<5	0.27	<1	18	14	32	2.11	<10	0.12	714	2	0.01	21	410	16	<5	<20	18	0.05	<10	24	<10	23	62
37	L21300N 4900E	10	0.5	1.03	15	150	5	0.24	<1	15	36	36	2.62	<10	0.62	390	3	0.01	36	360	20	<5	<20	14	0.09	<10	26	<10	15	73
38	L21300N 4925E	5	0.8	1.41	5	115	10	0.16	<1	16	43	23	3.18	<10	0.50	655	2	0.01	24	420	16	<5	<20	9	0.15	<10	44	<10	11	62
39	L21300N 4950E	10	0.3	1.40	5	110	10	0.27	<1	17	46	19	2.96	<10	0.62	764	<1	0.01	22	240	16	<5	<20	10	0.24	<10	31	<10	23	53
40	L21300N 4975E	5	0.2	1.44	5	110	10	0.43	<1	18	51	28	2.88	<10	0.90	489	<1	0.01	31	390	12	<5	<20	11	0.21	<10	25	<10	22	58

QC DATA:

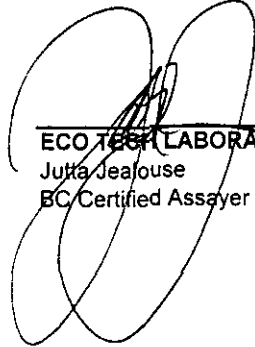
Repeat:

1	L21200N 4500E	<5	0.2	1.21	<5	240	5	0.50	<1	15	32	28	2.77	<10	0.50	708	2	0.01	17	580	32	<5	<20	37	0.09	<10	37	<10	28	61
10	L21200N 4725E	5	<0.2	0.78	5	90	10	0.13	<1	8	29	13	2.03	<10	0.30	213	2	0.01	13	290	20	<5	<20	6	0.11	<10	35	<10	6	47
19	L21200N 4950E	20	0.2	1.07	25	125	5	0.24	<1	22	38	64	3.29	<10	0.56	737	3	<0.01	42	520	24	<5	<20	15	0.11	<10	27	<10	15	89
28	L21300N 4675E	5	0.5	1.59	<5	90	10	0.15	<1	9	37	13	2.74	<10	0.32	175	2	0.01	13	310	16	<5	<20	7	0.17	<10	35	<10	10	33
36	L21300N 4875E	15	2.4	1.07	15	135	<5	0.27	<1	18	15	30	2.16	<10	0.13	724	2	0.01	22	440	16	<5	<20	17	0.06	<10	26	<10	24	61

Standard:

GEO'04	130	1.6	1.44	50	135	<5	1.26	<1	16	56	87	3.01	<10	0.77	547	<1	0.03	24	590	22	<5	<20	59	0.09	<10	55	<10	19	74
GEO'04	135	1.5	1.48	55	140	5	1.30	<1	16	58	88	3.09	<10	0.79	568	1	0.03	27	620	24	10	<20	53	0.09	<10	56	<10	19	76

IJ/jm
11/1500a
(LS/04


ECO TECH LABORATORY LTD.
 Jutta Jealous
 BC Certified Assayer

ECO TECH LABORATORY LTD.
10041 Dallas Drive
KAMLOOPS, B.C.
V2C 6T4

ICP CERTIFICATE OF ANALYSIS AK 2004-1502

NAVASOTA RESOURCES
#207 141 VICTORIA STREET
KAMLOOPS, BC
V2C 1Z5

Phone: 250-573-5700
Fax : 250-573-4557

No. of samples received: 40
Sample type: Soil
Project #: Not Indicated
Shipment #: Not Indicated

Values in ppm unless otherwise reported

Et #.	Tag #	Au (ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
1	L20800N 5025E	15	0.3	0.92	15	215	10	0.20	<1	13	29	14	2.78	<10	0.33	1742	1	0.01	21	520	20	<5	<20	12	0.13	<10	43	<10	4	69
2	L20800N 5050E	25	0.7	1.01	35	100	5	0.15	<1	11	25	19	2.96	<10	0.26	436	2	0.01	27	510	22	<5	<20	9	0.10	<10	42	<10	2	59
3	L20800N 5075E	35	4.2	3.25	90	625	<5	0.54	<1	42	84	147	6.08	10	0.94	3231	3	0.02	262	860	64	<5	<20	66	0.05	<10	66	<10	157	207
4	L20800N 5100E	5	1.0	1.04	<5	110	10	0.16	<1	10	35	22	2.66	<10	0.36	183	2	0.02	23	340	18	<5	<20	9	0.17	<10	41	<10	10	42
5	L20800N 5125E	10	0.5	1.15	15	140	5	0.13	<1	14	37	20	3.18	<10	0.36	967	2	0.01	24	810	18	<5	<20	5	0.13	<10	53	<10	2	55
6	L20800N 5150E	5	0.5	1.12	10	105	5	0.17	<1	10	30	20	2.60	<10	0.30	474	1	0.01	22	690	18	<5	<20	7	0.12	<10	41	<10	4	54
7	L20800N 5175E	5	0.4	1.54	5	135	5	0.20	<1	17	39	22	2.65	<10	0.46	625	1	0.01	25	300	16	<5	<20	9	0.16	<10	36	<10	17	60
8	L20800N 5200E	5	1.1	1.30	<5	140	<5	0.43	<1	16	32	30	2.39	<10	0.41	2133	<1	0.02	48	570	20	<5	<20	34	0.07	<10	30	<10	16	98
9	L20800N 5225E	-	1.2	1.22	10	95	5	0.55	<1	17	29	32	2.48	<10	0.42	913	1	0.02	53	530	20	<5	<20	43	0.09	<10	27	<10	17	85
10	L20800N 5250E	5	1.6	2.44	20	140	<5	0.45	<1	16	29	44	2.77	<10	0.35	1071	1	0.02	52	840	26	<5	<20	39	0.09	<10	22	<10	20	79
11	L20800N 5275E	40	0.5	0.68	15	130	<5	0.16	<1	10	16	21	2.94	<10	0.13	475	2	0.01	29	630	18	<5	<20	14	0.05	<10	39	<10	<1	59
12	L20800N 5300E	10	0.3	1.88	10	75	5	0.16	<1	11	42	21	2.78	<10	0.39	330	2	0.01	20	670	22	<5	<20	6	0.17	<10	31	<10	12	51
13	L20800N 5325E	10	0.8	0.71	30	135	5	0.18	<1	17	23	37	4.11	<10	0.27	830	3	<0.01	51	470	20	<5	<20	13	0.02	<10	38	<10	<1	103
14	L20800N 5350E	5	0.5	1.07	20	135	5	0.13	<1	20	31	33	4.11	<10	0.37	1037	2	0.01	42	430	26	<5	<20	6	0.12	<10	44	<10	<1	90
15	L20800N 5375E	5	0.9	1.16	20	195	5	0.19	<1	21	33	36	3.95	<10	0.38	945	2	0.01	50	520	24	<5	<20	14	0.08	<10	37	<10	12	88
16	L20800N 5400E	10	1.1	2.54	45	405	<5	0.81	<1	26	62	99	4.59	<10	0.65	1756	3	0.02	175	1400	36	<5	<20	81	0.03	<10	43	<10	47	130
17	L20800N 5425E	10	1.2	1.79	35	325	<5	0.74	<1	21	50	79	4.22	<10	0.46	905	3	0.02	144	890	30	<5	<20	69	0.03	<10	42	<10	21	117
18	L20800N 5450E	5	2.2	0.88	5	170	<5	1.72	<1	8	21	40	1.66	<10	0.38	211	1	0.02	69	730	14	<5	<20	141	0.02	<10	17	<10	19	33
19	L20800N 5475E	10	3.9	2.05	15	270	<5	0.99	<1	12	52	64	2.53	<10	0.54	596	1	0.02	101	1250	28	<5	<20	87	0.03	<10	35	<10	47	64
20	L20800N 5500E	5	2.7	1.96	15	220	<5	1.04	<1	13	38	49	2.38	<10	0.43	799	1	0.02	84	1220	20	<5	<20	89	0.03	<10	26	<10	38	69
21	L20900N 5025E	80	0.8	0.92	30	110	5	0.10	<1	16	26	25	3.32	<10	0.20	725	2	0.01	29	630	22	<5	<20	5	0.06	<10	41	<10	<1	71
22	L20900N 5050E	5	0.5	0.84	<5	75	5	0.17	<1	9	29	14	3.08	<10	0.25	342	2	0.01	14	540	24	<5	<20	7	0.17	<10	48	<10	5	47
23	L20900N 5075E	<5	0.4	0.84	<5	80	10	0.15	<1	11	37	13	2.97	<10	0.31	209	1	0.01	15	480	18	<5	<20	6	0.27	<10	43	<10	15	37
24	L20900N 5100E	15	0.3	1.50	10	105	10	0.34	<1	19	46	27	2.91	<10	0.65	477	<1	0.01	45	330	16	<5	<20	16	0.15	<10	30	<10	21	65
25	L20900N 5125E	35	<0.2	1.06	<5	90	10	0.29	<1	12	38	19	2.17	<10	0.49	291	<1	0.01	22	280	16	<5	<20	11	0.19	<10	25	<10	15	47

N	OTA	JURI	IC RTIF E OF .YSIK 200																	ECO		LAE		TOR						
Et #.	Tag #	Au (ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
26	L20900N 5150E	5	0.4	1.08	<5	115	10	0.41	<1	14	39	15	2.61	<10	0.45	512	1	0.01	19	280	20	<5	<20	19	0.22	<10	35	<10	16	49
27	L20900N 5175E	10	2.0	1.74	25	195	<5	0.54	<1	21	49	49	3.27	<10	0.59	943	1	0.01	104	600	28	<5	<20	42	0.14	<10	34	<10	54	107
28	L20900N 5200E	30	1.0	1.27	25	220	5	0.37	<1	25	36	39	3.36	<10	0.38	1894	1	0.01	86	740	36	<5	<20	26	0.09	<10	30	<10	23	135
29	L20900N 5225E	15	2.8	1.58	20	185	<5	1.03	<1	18	32	84	2.41	10	0.44	1877	1	0.02	127	1190	24	<5	<20	90	0.03	<10	28	<10	115	84
30	L20900N 5250E	5	0.8	0.90	10	170	<5	0.55	<1	17	30	47	2.96	<10	0.32	818	1	0.01	66	400	24	<5	<20	45	0.10	<10	28	<10	10	97
31	L20900N 5275E	15	0.9	1.31	25	140	<5	0.47	<1	22	26	57	3.26	<10	0.34	1138	2	0.02	89	930	22	<5	<20	38	0.05	<10	27	<10	26	95
32	L20900N 5300E	5	0.7	0.84	15	225	<5	0.49	<1	13	21	31	2.47	<10	0.22	1451	1	0.01	41	1130	18	<5	<20	29	0.05	<10	27	<10	2	97
33	L20900N 5325E	25	0.2	0.74	20	105	<5	0.25	<1	11	20	18	2.96	<10	0.22	483	2	0.01	29	750	18	<5	<20	22	0.04	<10	44	<10	<1	65
34	L20900N 5350E	15	1.0	1.46	45	130	<5	0.21	<1	19	40	46	3.69	<10	0.56	376	2	0.01	90	530	22	<5	<20	16	0.03	<10	41	<10	10	101
35	L20900N 5375E	15	3.6	2.42	30	190	<5	0.79	<1	21	28	96	2.66	<10	0.38	3648	1	0.03	107	1410	28	<5	<20	70	0.05	<10	20	<10	71	101
36	L20900N 5400E	20	3.5	2.82	25	150	<5	0.86	<1	16	38	109	2.29	10	0.40	2227	<1	0.02	135	1440	26	<5	<20	72	0.05	<10	15	<10	87	57
37	L20900N 5425E	5	2.2	1.51	15	165	<5	1.62	1	9	22	56	1.31	<10	0.46	2229	<1	0.02	71	2120	24	<5	<20	126	0.02	<10	15	<10	49	58
38	L20900N 5450E	5	1.0	1.75	10	100	5	1.02	<1	17	43	49	2.50	<10	0.65	561	2	0.02	62	600	18	<5	<20	79	0.08	<10	17	<10	27	56
39	L20900N 5475E	5	1.5	1.56	5	110	<5	1.38	<1	5	13	39	0.96	<10	0.34	655	<1	0.03	43	1590	14	<5	<20	108	0.03	<10	12	<10	28	22
40	L20900N 5500E	5	1.2	1.88	10	145	<5	1.33	<1	11	29	50	1.98	<10	0.51	577	1	0.02	48	930	18	<5	<20	104	0.04	<10	19	<10	25	54

QC DATA:

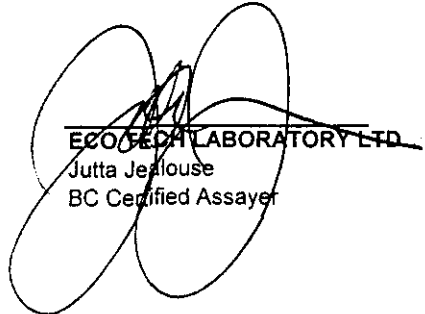
Repeat:

1	L20800N 5025E	5	0.3	0.95	20	210	10	0.20	<1	14	30	15	2.83	<10	0.33	1807	1	0.01	21	510	22	<5	<20	11	0.13	<10	46	<10	3	71
10	L20800N 5250E	5	1.8	2.57	20	150	<5	0.50	<1	17	30	46	2.88	<10	0.37	1117	1	0.02	54	890	28	<5	<20	44	0.08	<10	21	<10	23	82
19	L20800N 5475E	15	4.0	2.17	15	280	<5	0.99	<1	12	55	65	2.68	10	0.56	579	1	0.02	105	1290	28	<5	<20	88	0.05	<10	38	<10	49	68
28	L20900N 5200E	20	1.2	1.30	20	235	10	0.39	<1	25	37	40	3.28	<10	0.38	1915	1	0.01	87	830	34	<5	<20	27	0.10	<10	33	<10	23	135
36	L20900N 5400E	30	3.5	2.82	25	145	<5	0.88	<1	16	38	111	2.28	10	0.40	2348	<1	0.02	137	1490	28	<5	<20	71	0.05	<10	16	<10	86	58

Standard:

3EO'04	135	1.5	1.49	55	145	<5	1.33	<1	19	58	89	3.22	<10	0.79	588	<1	0.03	27	620	22	<5	<20	60	0.12	<10	59	<10	10	74
3EO'04	125	1.5	1.49	60	145	<5	1.32	<1	19	57	89	3.28	<10	0.78	584	1	0.03	27	630	24	<5	<20	61	0.09	<10	55	<10	10	76

J/sc
W/1512/1500a
LS/04


ECO FEDI LABORATORY LTD.
 Jutta Jeilouse
 BC Certified Assayer

ECO TECH LABORATORY LTD.
10041 Dallas Drive
KAMLOOPS, B.C.
V2C 6T4

ICP CERTIFICATE OF ANALYSIS AK 2004-1593

NAVASOTA RESOURCES
#207 141 VICTORIA STREET
KAMLOOPS, BC
V2C 1Z5

Phone: 250-573-5700
Fax : 250-573-4557

No. of samples received: 117
Sample type: Soil
Project #: Not Indicated
Shipment #: Not Indicated

Values in ppm unless otherwise reported

Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
1	B.L. 5000E 22400N	<5	1.2	1.79	<5	95	5	0.18	<1	16	57	30	3.59	<10	0.55	361	3	0.01	27	470	28	<5	<20	4	0.16	<10	75	<10	2	56
2	B.L. 5000E 22425N	15	0.4	1.78	<5	85	15	0.37	<1	18	71	24	3.90	<10	0.84	498	2	0.01	35	430	20	<5	<20	5	0.24	<10	49	<10	2	58
3	B.L. 5000E 22450N	<5	0.5	1.06	<5	45	<5	0.16	<1	11	26	12	2.09	<10	0.19	552	1	0.02	9	400	16	<5	<20	2	0.13	<10	33	<10	<1	27
4	B.L. 5000E 22475N	<5	0.5	2.42	<5	60	5	0.33	<1	16	71	20	4.06	<10	0.74	449	<1	0.01	28	470	22	<5	<20	3	0.22	<10	53	<10	4	58
5	B.L. 5000E 22500N	<5	0.4	0.67	<5	45	5	0.14	<1	7	21	11	2.38	<10	0.13	234	1	0.01	8	410	16	<5	<20	1	0.18	<10	46	<10	<1	25
6	B.L. 5000E 22525N	<5	0.4	0.77	<5	60	<5	0.14	<1	8	28	11	2.63	<10	0.20	124	1	0.01	11	350	14	<5	<20	<1	0.21	<10	59	<10	<1	25
7	B.L. 5000E 22550N	<5	0.3	0.72	<5	45	5	0.15	<1	7	27	10	2.51	<10	0.17	156	2	0.01	9	360	16	<5	<20	<1	0.16	<10	55	<10	<1	26
8	B.L. 5000E 22575N	<5	0.6	0.95	<5	45	5	0.16	<1	9	31	10	2.98	<10	0.22	275	<1	0.01	9	580	16	<5	<20	<1	0.18	<10	42	<10	<1	28
9	B.L. 5000E 22600N	<5	0.6	1.24	<5	45	10	0.15	<1	9	40	15	3.68	<10	0.31	291	3	0.01	14	380	20	<5	<20	<1	0.14	<10	51	<10	<1	34
10	B.L. 5000E 22625N	<5	0.9	1.45	<5	75	5	0.16	<1	11	34	18	3.17	<10	0.28	306	3	0.01	15	520	22	<5	<20	4	0.14	<10	45	<10	3	37
11	B.L. 5000E 22650N	<5	0.2	1.18	<5	110	10	0.19	<1	11	41	17	3.35	<10	0.35	312	2	0.02	18	430	22	<5	<20	3	0.19	<10	61	<10	<1	46
12	B.L. 5000E 22675N	<5	0.7	1.22	<5	165	5	0.25	<1	11	37	24	2.77	<10	0.37	273	2	0.01	22	450	16	<5	<20	10	0.15	<10	52	<10	10	54
13	B.L. 5000E 22700N	<5	1.4	2.85	10	270	<5	0.23	<1	17	78	92	4.20	<10	0.80	403	3	0.02	71	700	34	<5	<20	18	0.11	<10	103	<10	22	181
14	B.L. 5000E 22725N	5	2.3	3.37	10	180	<5	0.66	2	14	54	118	3.16	20	0.51	713	1	0.02	110	920	36	<5	<20	83	0.09	<10	59	<10	84	250
15	B.L. 5000E 22750N	<5	0.4	1.79	<5	135	5	0.56	<1	13	46	26	3.40	<10	0.51	627	2	0.02	28	430	26	<5	<20	50	0.14	<10	54	<10	8	88
16	B.L. 5000E 22775N	15	0.2	0.95	<5	110	10	0.25	<1	10	36	14	2.83	<10	0.35	193	2	0.01	17	280	20	<5	<20	5	0.20	<10	60	<10	<1	45
17	B.L. 5000E 22800N	<5	0.7	2.20	5	195	<5	0.45	<1	15	44	41	3.21	<10	0.47	849	2	0.02	27	540	28	<5	<20	38	0.12	<10	72	<10	15	67
18	B.L. 5000E 22825N	<5	0.2	0.72	<5	125	<5	0.18	<1	7	22	9	2.06	<10	0.21	219	1	0.01	10	250	16	<5	<20	8	0.15	<10	34	<10	<1	29
19	B.L. 5000E 22850N	<5	0.3	1.42	<5	90	10	0.19	<1	12	43	20	3.76	<10	0.46	234	2	0.02	20	290	22	<5	<20	5	0.21	<10	45	<10	<1	55
20	B.L. 5000E 22875N	<5	0.4	1.32	<5	90	5	0.20	<1	13	44	17	4.13	<10	0.45	217	2	0.01	18	330	22	<5	<20	4	0.24	<10	58	<10	<1	52
21	B.L. 5000E 22900N	<5	0.3	0.91	<5	90	10	0.26	<1	10	33	14	3.36	<10	0.28	171	1	0.01	14	320	18	<5	<20	12	0.22	<10	56	<10	<1	44
22	B.L. 5000E 22925N	<5	0.3	1.00	<5	80	5	0.16	<1	10	38	25	3.70	<10	0.28	123	1	0.01	14	260	18	<5	<20	4	0.21	<10	49	<10	<1	41
23	B.L. 5000E 22950N	<5	1.1	1.74	<5	130	<5	0.71	3	11	29	41	2.75	<10	0.35	728	2	0.02	19	500	22	<5	<20	69	0.10	<10	44	<10	15	80
24	B.L. 5000E 22975N	<5	0.9	3.26	25	225	<5	0.82	<1	17	65	49	3.12	<10	0.69	1345	2	0.02	48	1140	34	<5	<20	53	0.07	<10	70	<10	28	120
25	B.L. 5000E 23000N	<5	0.6	1.38	<5	135	5	0.29	<1	15	36	27	3.16	<10	0.39	272	2	0.02	19	250	20	<5	<20	20	0.17	<10	56	<10	9	42

Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
26	B.L. 5000E 23025N	<5	0.8	1.41	<5	130	<5	0.15	<1	8	23	35	2.01	<10	0.16	85	1	0.02	18	430	16	<5	<20	9	0.06	<10	33	<10	21	25
27	B.L. 5000E 23050N	<5	0.2	0.63	5	180	<5	1.62	<1	1	6	21	0.62	<10	0.21	45	<1	0.02	9	1430	4	<5	<20	92	<0.01	<10	18	<10	8	8
28	B.L. 5000E 23075N	<5	0.9	1.31	5	195	<5	1.42	<1	15	25	21	1.74	<10	0.40	221	1	0.02	18	850	20	<5	<20	129	0.03	<10	34	<10	21	29
29	B.L. 5000E 23100N	<5	0.6	2.12	<5	80	<5	0.23	<1	30	32	48	2.72	<10	0.22	323	1	0.02	19	400	20	<5	<20	8	0.12	<10	45	<10	24	32
30	B.L. 5000E 23125N	<5	0.5	2.12	<5	85	<5	0.23	<1	25	38	46	2.79	<10	0.31	296	<1	0.02	20	360	22	<5	<20	8	0.15	<10	44	<10	23	35
31	B.L. 5000E 23150N	<5	0.3	1.17	5	175	<5	0.38	<1	6	20	37	3.03	<10	0.12	79	2	0.02	10	390	18	<5	<20	18	0.10	<10	36	<10	3	34
32	B.L. 5000E 23175N	<5	0.3	1.46	5	200	<5	0.46	<1	7	21	41	3.34	<10	0.14	91	2	0.01	11	440	20	<5	<20	22	0.11	<10	40	<10	5	39
33	B.L. 5000E 23200N	<5	0.6	2.35	15	215	<5	0.93	<1	9	25	52	2.12	<10	0.25	1850	1	0.02	18	1250	22	<5	<20	52	0.03	<10	52	<10	20	50
34	B.L. 5000E 23225N	<5	0.2	1.06	<5	65	<5	0.19	<1	13	23	21	2.56	<10	0.25	1532	1	0.02	13	360	20	<5	<20	7	0.10	<10	38	<10	<1	42
35	B.L. 5000E 23250N	<5	<0.2	0.48	<5	50	<5	0.11	<1	6	19	8	1.77	<10	0.14	182	<1	0.02	6	260	16	<5	<20	<1	0.14	<10	38	<10	<1	29
36	B.L. 5000E 23275N	<5	0.5	3.34	25	285	<5	0.72	<1	22	49	48	3.24	<10	0.43	2072	<1	0.02	41	1210	36	<5	<20	46	0.05	<10	69	<10	23	145
37	B.L. 5000E 23300N	<5	0.8	3.38	30	330	<5	1.54	1	20	44	58	2.33	10	0.41	2212	2	0.02	40	1930	32	<5	<20	101	0.03	<10	55	<10	44	146
38	B.L. 5000E 23325N	<5	<0.2	0.62	<5	45	5	0.16	<1	8	22	10	2.29	<10	0.17	123	1	0.01	10	180	10	<5	<20	2	0.18	<10	42	<10	<1	24
39	B.L. 5000E 23350N	10	0.4	1.03	10	60	5	0.08	<1	6	11	9	2.28	<10	0.04	75	2	0.02	12	230	24	<5	<20	3	0.09	<10	29	<10	<1	30
40	B.L. 5000E 23375N	<5	0.7	1.34	<5	45	5	0.14	<1	7	31	12	1.92	<10	0.21	105	1	0.02	12	290	36	<5	<20	5	0.10	<10	11	<10	2	25
41	B.L. 5000E 23400N	<5	0.2	0.38	<5	45	<5	0.09	<1	4	14	7	1.04	<10	0.05	46	<1	0.02	5	240	32	<5	<20	4	0.06	<10	14	<10	<1	15
42	B.L. 5000E 23425N	<5	0.3	2.78	25	190	<5	0.57	<1	14	54	31	2.70	<10	0.63	700	2	0.01	38	800	34	<5	<20	25	0.08	<10	61	<10	23	90
43	B.L. 5000E 23450N	<5	0.3	2.58	15	145	5	0.42	<1	27	83	73	4.24	<10	1.16	600	2	0.01	65	410	28	<5	<20	7	0.14	<10	76	<10	13	62
44	B.L. 5000E 23475N	<5	0.2	1.85	5	110	5	0.24	<1	17	59	29	3.67	<10	0.80	743	2	0.01	33	450	24	<5	<20	3	0.14	<10	68	<10	<1	60
45	B.L. 5000E 23500N	5	0.3	1.91	<5	145	5	0.28	<1	14	55	25	4.46	<10	0.56	579	3	0.02	24	420	22	<5	<20	7	0.16	<10	62	<10	<1	61
46	B.L. 5000E 23525N	<5	0.2	2.20	15	195	<5	0.34	<1	25	92	49	4.29	<10	1.13	812	2	0.01	54	420	34	<5	<20	10	0.12	<10	77	<10	8	81
47	B.L. 5000E 23550N	<5	0.4	3.84	15	245	5	0.17	<1	27	78	73	4.68	<10	0.77	1232	2	0.02	53	420	40	<5	<20	5	0.14	<10	72	<10	11	109
48	B.L. 5000E 23575N	5	0.2	1.58	<5	145	10	0.24	<1	19	61	27	3.99	<10	0.86	852	3	0.01	30	450	24	<5	<20	1	0.17	<10	60	<10	2	62
49	B.L. 5000E 23600N	15	1.5	4.12	20	270	<5	0.76	<1	24	90	101	3.87	10	0.86	922	1	0.02	65	720	38	<5	<20	44	0.13	<10	50	<10	46	99
50	B.L. 5000E 23625N	5	0.4	2.33	10	195	10	0.40	<1	21	69	32	3.78	<10	1.05	474	3	0.01	46	230	26	<5	<20	17	0.14	<10	52	<10	10	58
51	B.L. 5000E 23650N	5	0.4	2.21	15	245	<5	0.23	<1	18	68	38	4.43	<10	0.72	367	3	0.01	42	300	28	<5	<20	12	0.07	<10	90	<10	2	65
52	B.L. 5000E 23675N	5	0.3	1.47	10	130	<5	0.16	<1	11	48	30	3.71	<10	0.35	315	2	0.01	18	360	20	<5	<20	6	0.12	<10	60	<10	<1	52
53	B.L. 5000E 23700N	5	0.3	1.23	<5	125	5	0.18	<1	13	55	19	4.18	<10	0.60	341	3	0.01	24	270	20	<5	<20	4	0.17	<10	81	<10	<1	61
54	B.L. 5000E 23725N	<5	1.0	2.99	10	185	<5	0.87	<1	17	36	59	3.15	<10	0.25	1142	2	0.02	27	700	32	<5	<20	64	0.09	<10	36	<10	24	62
55	B.L. 5000E 23750N	5	0.2	1.80	5	125	10	0.19	<1	13	60	26	4.36	<10	0.53	301	2	0.01	26	340	24	<5	<20	6	0.14	<10	71	<10	<1	63
56	B.L. 5000E 23775N	<5	0.4	2.05	10	130	10	0.23	<1	17	69	36	4.55	<10	0.84	327	2	0.01	40	360	24	<5	<20	6	0.17	<10	74	<10	2	76
57	B.L. 5000E 23800N	5	0.5	2.10	10	130	<5	0.26	<1	17	73	38	4.56	<10	0.93	326	2	0.01	44	350	24	<5	<20	10	0.14	<10	73	<10	4	80
58	L21200N 5025E	5	0.5	0.79	<5	75	<5	0.17	<1	11	27	9	2.53	<10	0.26	440	<1	0.01	11	340	14	<5	<20	2	0.19	<10	34	<10	<1	30
59	L21200N 5050E	15	0.3	1.46	<5	90	5	0.27	<1	16	46	21	3.39	<10	0.58	460	<1	0.01	26	300	18	<5	<20	3	0.19	<10	31	<10	2	49
60	L21200N 5075E	5	0.3	1.68	<5	80	5	0.31	<1	18	57	18	3.68	<10	0.86	420	<1	<0.01	31	220	18	<5	<20	<1	0.24	<10	34	<10	4	58
61	L21200N 5100E	10	0.3	1.64	15	80	5	0.26	<1	20	52	31	4.16	<10	0.75	510	<1	<0.01	42	320	26	<5	<20	<1	0.21	<10	42	<10	2	71
62	L21200N 5125E	5	0.3	1.49	<5	90	<5	0.24	<1	13	46	22	3.58	<10	0.57	244	<1	0.01	24	250	18	<5	<20	2	0.22	<10	36	<10	<1	56
63	L21200N 5150E	<5	0.2	0.14	<5	40	<5	1.64	<1	<1	2	9	0.27	<10	0.33	123	<1	0.02	9	740	2	<5	<20	98	<0.01	<10	4	<10	<1	8
64	L21200N 5175E	10	0.5	1.08	5	80	5	0.19	<1	9	29	12	3.18	<10	0.29	206	2	0.01	18	380	20	<5	<20	3	0.14	<10	40	<10	<1	52
65	L21200N 5200E	5	0.4	0.73	<5	120	<5	0.30	<1	9	23	8	2.42	<10	0.25	863	<1	0.01	11	390	20	<5	<20	13	0.20	<10	37	<10	<1	37

Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
66	L21200N 5225E	5	0.5	0.69	5	100	<5	0.15	<1	7	22	17	2.60	<10	0.16	214	2	0.01	19	410	18	<5	<20	3	0.09	<10	67	<10	<1	47
67	L21200N 5250E	5	0.3	0.64	<5	105	<5	0.20	<1	2	14	7	0.56	<10	0.10	48	<1	0.01	9	240	14	<5	<20	8	0.06	<10	2	<10	3	18
68	L21200N 5275E	5	0.9	1.35	10	115	5	0.19	<1	10	41	18	4.24	<10	0.36	337	2	0.01	21	420	20	<5	<20	4	0.16	<10	53	<10	<1	52
69	L21200N 5300E	5	1.0	1.10	5	115	5	0.12	<1	8	20	17	2.95	<10	0.14	222	2	0.01	13	390	18	<5	<20	2	0.08	<10	41	<10	3	35
70	L21200N 5325E	5	1.0	0.98	<5	220	<5	0.32	<1	7	22	33	2.55	<10	0.20	120	2	0.01	20	460	18	<5	<20	18	0.08	<10	37	<10	6	36
71	L21200N 5350E	10	0.5	0.78	10	200	5	0.22	<1	10	24	23	2.86	<10	0.21	1105	2	0.01	18	670	20	<5	<20	7	0.08	<10	46	<10	<1	57
72	L21200N 5375E	5	0.9	0.79	<5	290	<5	0.54	<1	7	18	18	1.91	<10	0.19	896	2	0.02	19	590	22	<5	<20	35	0.06	<10	39	<10	3	43
73	L21200N 5400E	<5	0.8	2.47	10	310	<5	0.77	<1	15	43	43	2.84	10	0.39	2779	2	0.02	31	1020	26	<5	<20	50	0.04	<10	76	<10	24	48
74	L21200N 5425E	10	0.3	1.39	<5	125	5	0.37	<1	16	37	26	2.95	<10	0.33	437	3	0.01	18	370	20	<5	<20	17	0.14	<10	62	<10	5	35
75	L21200N 5450E	5	0.5	2.07	<5	195	5	0.48	<1	20	64	44	3.85	<10	0.75	487	2	0.02	37	440	26	<5	<20	19	0.17	<10	53	<10	8	67
76	L21200N 5475E	5	0.7	1.20	<5	160	<5	0.30	<1	13	30	29	2.78	<10	0.25	238	2	0.01	18	300	20	<5	<20	13	0.14	<10	52	<10	8	36
77	L21200N 5500E	10	0.8	2.18	10	240	<5	0.34	<1	25	55	53	3.84	<10	0.58	1221	3	0.02	41	540	28	<5	<20	15	0.09	<10	87	<10	7	74
78	L21500N 4500E	40	0.3	1.42	<5	165	<5	0.39	<1	12	27	24	3.41	<10	0.43	1027	2	0.01	16	680	24	<5	<20	12	0.10	<10	41	<10	9	60
79	L21500N 4525E	45	0.3	1.23	<5	95	10	0.17	<1	12	31	17	3.96	<10	0.36	419	2	0.01	15	330	20	<5	<20	2	0.22	<10	54	<10	<1	44
80	L21500N 4550E	15	0.2	0.87	<5	110	<5	0.16	<1	9	26	12	3.25	<10	0.26	392	1	0.01	11	360	18	<5	<20	2	0.18	<10	53	<10	<1	39
81	L21500N 4575E	90	0.3	0.90	<5	190	<5	0.13	<1	10	27	17	3.67	<10	0.22	532	2	0.01	10	460	16	<5	<20	3	0.16	<10	61	<10	<1	45
82	L21500N 4600E	70	0.3	1.47	<5	105	10	0.13	<1	11	35	17	4.46	<10	0.32	290	2	0.01	13	380	20	<5	<20	2	0.21	<10	74	<10	<1	42
83	L21500N 4625E	10	0.3	2.57	15	130	15	0.20	<1	18	53	26	5.58	<10	0.58	398	4	0.01	19	280	26	<5	<20	<1	0.25	<10	72	<10	8	46
84	L21500N 4650E	10	0.4	1.42	<5	190	<5	0.54	<1	16	40	31	3.53	<10	0.39	716	2	0.02	14	430	22	<5	<20	19	0.13	<10	49	<10	22	47
85	L21500N 4675E	5	0.3	1.06	<5	85	10	0.16	<1	11	31	13	3.60	<10	0.27	280	1	0.01	13	230	18	<5	<20	<1	0.23	<10	55	<10	<1	36
86	L21500N 4700E	10	0.2	1.34	<5	125	15	0.36	<1	14	46	22	3.51	<10	0.62	546	3	0.01	23	440	18	<5	<20	7	0.21	<10	46	<10	<1	52
87	L21500N 4725E	25	0.7	1.54	5	150	<5	0.45	<1	14	34	25	2.62	<10	0.31	434	2	0.01	13	390	28	<5	<20	16	0.12	<10	42	<10	39	39
88	L21500N 4750E	5	0.2	0.67	<5	60	10	0.10	<1	7	18	9	2.36	<10	0.12	107	1	0.01	7	280	14	<5	<20	1	0.17	<10	44	<10	<1	22
89	L21500N 4775E	<5	0.3	1.62	<5	270	10	0.27	<1	11	36	21	4.25	<10	0.33	521	3	0.01	14	520	20	<5	<20	8	0.20	<10	47	<10	<1	66
90	L21500N 4800E	<5	0.4	0.48	<5	200	<5	0.18	<1	6	17	10	2.10	<10	0.11	388	1	0.01	6	270	14	<5	<20	6	0.17	<10	54	<10	<1	33
91	L21500N 4825E	5	0.3	1.04	<5	245	5	0.15	<1	12	18	24	2.61	<10	0.13	508	2	0.02	10	370	18	<5	<20	9	0.11	<10	43	<10	5	25
92	L21500N 4850E	5	0.3	0.58	<5	130	5	0.09	<1	7	24	10	2.65	<10	0.15	139	1	0.01	10	300	14	<5	<20	<1	0.22	<10	68	<10	<1	30
93	L21500N 4875E	10	1.7	1.96	5	345	<5	0.28	<1	3	18	67	1.46	<10	0.16	363	<1	0.02	18	850	22	<5	<20	32	0.04	<10	26	<10	25	26
94	L21500N 4900E	10	0.8	0.52	<5	160	<5	0.12	<1	5	17	15	2.27	<10	0.09	134	2	0.01	7	320	14	<5	<20	7	0.14	<10	52	<10	<1	24
95	L21500N 4925E	5	1.1	1.32	10	355	5	0.34	<1	12	21	31	2.35	<10	0.19	1444	2	0.02	19	580	26	<5	<20	32	0.09	<10	39	<10	12	50
96	L21500N 4950E	20	0.6	0.47	<5	725	<5	1.04	<1	6	23	14	2.36	<10	0.18	2488	<1	0.01	12	510	14	<5	<20	62	0.15	<10	58	<10	<1	114
97	L21500N 4975E	10	0.7	0.85	<5	235	10	0.40	<1	14	36	23	3.29	<10	0.33	613	3	0.01	16	590	18	<5	<20	22	0.22	<10	54	<10	2	48
98	L21500N 5025E	5	0.6	1.81	<5	145	10	0.17	<1	17	53	29	4.42	<10	0.53	855	3	0.01	31	450	22	<5	<20	1	0.24	<10	63	<10	<1	81
99	L21500N 5050E	25	0.3	0.40	15	45	<5	0.02	<1	6	7	16	3.16	<10	0.03	117	3	0.01	21	460	24	<5	<20	<1	0.03	<10	44	<10	<1	51
100	L21500N 5075E	<5	0.3	0.62	<5	75	<5	0.11	<1	6	20	11	2.04	<10	0.13	168	1	0.01	8	340	14	<5	<20	2	0.17	<10	50	<10	<1	19
101	L21500N 5100E	<5	0.3	1.32	5	115	5	0.17	<1	19	42	24	3.59	<10	0.50	881	3	0.01	31	330	24	<5	<20	2	0.18	<10	60	<10	4	65
102	L21500N 5125E	<5	0.3	0.88	10	55	10	0.10	<1	10	32	14	3.52	<10	0.31	195	2	0.01	20	340	18	<5	<20	<1	0.25	10	67	<10	<1	40
103	L21500N 5150E	<5	0.3	0.77	<5	135	<5	0.27	<1	8	23	18	2.12	<10	0.22	386	<1	0.02	11	400	14	<5	<20	15	0.13	<10	48	<10	10	34
104	L21500N 5175E	5	0.4	0.89	<5	90	10	0.15	<1	10	34	23	3.67	<10	0.24	324	2	0.01	14	420	18	<5	<20	4	0.25	<10	68	<10	<1	40
105	L21500N 5200E	30	0.5	0.67	<5	105	10	0.19	<1	9	28	10	2.97	<10	0.21	236	2	0.01	11	450	18	<5	<20	5	0.25	<10	64	<10	<1	40

Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
106	L21500N 5225E	<5	0.4	1.71	5	95	10	0.28	<1	16	56	20	4.11	<10	0.73	475	2	0.01	26	890	20	<5	<20	1	0.23	<10	53	<10	2	81
107	L21500N 5250E	<5	0.5	0.82	<5	165	<5	0.25	<1	10	21	14	2.30	<10	0.16	2055	1	0.02	9	430	16	<5	<20	8	0.16	<10	53	<10	3	31
108	L21500N 5350E	5	0.3	1.00	<5	60	5	0.11	<1	11	27	11	3.59	<10	0.25	775	1	0.01	16	730	18	<5	<20	<1	0.21	<10	53	<10	<1	40
109	L21500N 5375E	<5	0.6	0.88	<5	60	<5	0.11	<1	7	17	12	2.94	<10	0.08	342	<1	0.02	4	400	18	<5	<20	2	0.20	<10	62	<10	<1	22
110	L21500N 5400E	<5	1.0	1.53	<5	155	<5	0.26	<1	21	28	29	2.57	<10	0.22	548	<1	0.02	13	500	20	<5	<20	9	0.18	<10	54	<10	20	32
111	L21500N 5425E	<5	1.3	1.84	<5	325	<5	0.61	<1	18	36	71	2.35	10	0.25	2372	2	0.02	23	1180	22	<5	<20	40	0.04	<10	74	<10	34	35
112	L21500N 5450E	5	0.3	0.67	<5	75	<5	0.10	<1	7	18	11	2.79	<10	0.11	137	1	0.01	9	210	14	<5	<20	1	0.18	<10	54	<10	<1	27
113	L21500N 5475E	5	0.5	0.56	10	55	<5	0.08	<1	5	12	9	1.95	<10	0.07	114	<1	0.01	8	230	18	<5	<20	2	0.15	<10	50	<10	<1	23
114	L21500N 5500E	10	0.8	1.01	15	130	10	0.12	<1	11	22	18	4.44	<10	0.16	305	2	0.01	18	360	22	<5	<20	5	0.16	<10	65	<10	<1	56
115	L21500N 50275E	<5	0.3	1.29	5	80	<5	0.14	<1	12	36	21	2.55	<10	0.41	163	2	0.01	19	210	24	<5	<20	<1	0.24	<10	47	<10	5	54
116	L21500N 50300E	<5	0.5	1.05	<5	85	5	0.14	<1	8	23	19	2.38	<10	0.21	221	2	0.02	12	510	20	<5	<20	3	0.11	<10	44	<10	1	31
117	L21500N 50325E	<5	0.4	1.32	<5	80	15	0.15	<1	10	36	16	3.98	<10	0.31	232	2	0.01	15	520	20	<5	<20	3	0.22	<10	69	<10	<1	39

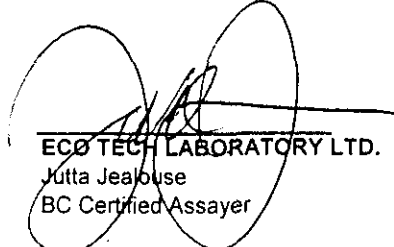
QC DATA:

Repeat:

1	B.L. 5000E 22400N	5	1.4	1.68	<5	90	5	0.15	<1	14	54	28	3.46	<10	0.52	365	4	0.01	26	450	28	<5	<20	2	0.16	<10	73	<10	2	54
10	B.L. 5000E 22625N	<5	0.9	1.46	<5	70	<5	0.16	<1	11	34	18	3.16	<10	0.30	308	3	0.01	16	480	20	<5	<20	3	0.14	<10	50	<10	3	37
19	B.L. 5000E 22850N	<5	0.3	1.38	<5	90	5	0.20	<1	11	43	19	3.67	<10	0.48	235	1	0.01	18	270	20	<5	<20	5	0.23	<10	52	<10	<1	53
28	B.L. 5000E 23075N	<5	0.9	1.30	5	200	<5	1.55	1	16	24	21	1.63	<10	0.40	230	1	0.02	19	870	20	<5	<20	142	0.02	<10	33	<10	23	27
36	B.L. 5000E 23275N	<5	0.5	3.16	20	260	<5	0.67	<1	21	47	45	3.08	<10	0.43	1955	2	0.02	39	1100	34	<5	<20	39	0.05	<10	70	<10	21	139
45	B.L. 5000E 23500N	<5	0.3	1.82	<5	135	5	0.25	<1	14	57	23	4.39	<10	0.57	557	2	0.01	24	380	22	<5	<20	5	0.15	<10	65	<10	<1	59
54	B.L. 5000E 23725N	5	1.0	3.06	10	185	<5	0.89	<1	17	35	61	3.12	<10	0.23	1184	3	0.02	26	670	36	<5	<20	67	0.08	<10	37	<10	26	62
63	L21200N 5150E		0.2	0.13	<5	40	<5	1.68	<1	<1	2	9	0.26	<10	0.33	115	<1	0.02	8	760	<2	5	<20	101	<0.01	<10	4	<10	<1	8
64	L21200N 5175E	10																												
71	L21200N 5350E	<5	0.5	0.80	10	205	<5	0.23	<1	10	24	22	2.80	<10	0.21	1077	2	0.01	18	680	20	<5	<20	6	0.08	<10	47	<10	<1	56
74	L21200N 5425E	5																												
80	L21500N 4550E	<5	0.3	0.90	<5	115	5	0.17	<1	10	26	12	3.27	<10	0.26	386	2	0.01	11	390	20	<5	<20	3	0.21	<10	52	<10	<1	39
89	L21500N 4775E	<5	0.4	1.67	<5	280	5	0.29	<1	12	37	21	4.32	<10	0.34	561	3	0.01	17	550	22	<5	<20	8	0.23	<10	48	<10	<1	69
98	L21500N 5025E	5	0.6	1.92	5	150	10	0.19	<1	18	54	30	4.50	<10	0.56	848	2	0.01	32	480	24	<5	<20	2	0.24	<10	62	<10	<1	84
106	L21500N 5225E	<5	0.3	1.72	<5	100	10	0.28	<1	16	55	20	4.06	<10	0.75	485	3	0.01	28	840	20	<5	<20	2	0.25	<10	59	<10	1	80

Standard:

GEO'04		140	1.4	1.49	50	135	<5	1.32	<1	16	56	86	3.64	<10	0.78	566	<1	0.02	28	610	26	<5	<20	57	0.11	<10	70	<10	10	69
GEO'04		135	1.5	1.53	45	145	<5	1.36	<1	16	58	87	3.72	<10	0.81	577	<1	0.03	29	630	22	<5	<20	61	0.10	<10	69	<10	9	70
GEO'04		140	1.6	1.57	55	155	<5	1.38	<1	17	60	88	3.84	<10	0.83	593	<1	0.03	27	650	24	<5	<20	60	0.11	<10	68	<10	9	71


ECO TECH LABORATORY LTD.
 Jutta Jealous
 BC Certified Assayer

ECO TECH LABORATORY LTD.
10041 Dallas Drive
KAMLOOPS, B.C.
V2C 6T4

ICP CERTIFICATE OF ANALYSIS AK 2004-1594

NAVASOTA RESOURCES
#207 141 VICTORIA STREET
KAMLOOPS, BC
V2C 1Z5

Phone: 250-573-5700

Fax : 250-573-4557

No. of samples received: 80
Sample type: Soil
Project #: Not Indicated
Shipment #: Not Indicated

Values in ppm unless otherwise reported

Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
1	L21400N 4500E	225	0.2	1.28	25	150	5	0.39	<1	25	8	26	6.95	<10	0.22	3527	5	0.02	4	1000	34	<5	<20	14	0.05	<10	43	<10	2	76
2	L21400N 4525E	5	<0.2	1.71	5	65	10	0.24	<1	17	48	18	4.52	<10	0.74	466	1	<0.01	21	460	20	<5	<20	<1	0.28	<10	52	<10	<1	63
3	L21400N 4550E	<5	0.2	1.63	5	55	<5	0.18	<1	15	40	19	3.79	<10	0.66	370	1	<0.01	20	300	18	<5	<20	<1	0.27	<10	41	<10	<1	47
4	L21400N 4575E	<5	0.3	0.91	<5	85	5	0.09	<1	6	13	14	2.78	<10	0.11	346	2	0.01	7	450	16	<5	<20	1	0.11	<10	46	<10	<1	29
5	L21400N 4600E	<5	0.3	0.62	<5	90	10	0.09	<1	7	15	11	2.81	<10	0.12	259	2	0.01	6	300	16	<5	<20	2	0.20	<10	57	<10	<1	28
6	L21400N 4625E	<5	0.2	1.21	<5	110	10	0.19	<1	11	27	13	3.50	<10	0.29	762	1	0.01	11	440	18	<5	<20	2	0.25	<10	72	<10	<1	47
7	L21400N 4650E	5	0.3	1.37	10	125	10	0.27	<1	13	37	22	3.16	<10	0.46	371	3	0.01	19	410	18	<5	<20	6	0.19	<10	60	<10	2	42
8	L21400N 4675E	10	<0.2	1.77	20	155	5	0.09	<1	21	56	54	4.45	<10	0.67	530	4	<0.01	41	390	26	<5	<20	4	0.09	<10	79	<10	<1	89
9	L21400N 4700E	<5	0.2	3.16	10	380	10	0.18	<1	20	108	31	4.96	<10	1.38	544	3	<0.01	48	370	26	<5	<20	4	0.17	<10	116	<10	9	55
10	L21400N 4725E	35	0.2	2.10	20	165	<5	0.23	<1	23	64	41	4.23	<10	0.91	678	3	0.01	38	280	22	<5	<20	2	0.15	<10	67	<10	3	57
11	L21400N 4750E	<5	0.3	0.98	5	110	<5	0.13	<1	14	32	12	3.40	<10	0.35	1096	1	0.01	15	320	14	<5	<20	<1	0.14	<10	82	<10	<1	39
12	L21400N 4775E	<5	0.2	1.57	5	95	10	0.25	<1	16	51	19	5.09	<10	0.59	363	4	0.01	20	400	20	<5	<20	4	0.21	<10	103	<10	5	53
13	L21400N 4800E	<5	0.2	1.80	10	95	15	0.17	<1	16	59	24	5.24	<10	0.64	263	4	0.01	23	240	20	<5	<20	2	0.25	<10	78	<10	<1	50
14	L21400N 4825E	<5	0.5	1.93	10	130	<5	0.26	<1	18	26	42	2.68	<10	0.13	370	<1	0.02	11	360	22	<5	<20	9	0.09	<10	29	<10	27	29
15	L21400N 4850E	40	0.4	2.30	20	235	5	0.41	<1	22	80	62	4.95	<10	0.90	505	1	0.01	42	320	22	<5	<20	6	0.22	<10	50	<10	42	81
16	L21400N 4875E	<5	0.7	1.40	10	235	<5	1.78	<1	9	39	69	1.96	<10	0.31	1193	1	0.02	20	1080	16	<5	<20	56	0.03	<10	42	<10	33	76
17	L21400N 4900E	<5	0.3	2.00	15	225	<5	0.84	<1	14	43	38	3.15	<10	0.47	744	1	0.01	27	620	22	<5	<20	27	0.09	<10	54	<10	23	92
18	L21400N 4925E	<5	0.3	1.19	<5	155	5	0.17	<1	16	44	20	3.88	<10	0.48	339	2	0.01	19	200	18	<5	<20	3	0.30	<10	53	<10	<1	41
19	L21400N 4950E	<5	0.3	1.29	<5	160	10	0.13	<1	16	45	20	4.06	<10	0.50	572	2	0.01	20	380	18	<5	<20	1	0.30	<10	71	<10	<1	56
20	L21400N 4975E	<5	1.0	1.36	5	535	<5	0.39	<1	17	31	45	2.73	10	0.30	2311	2	0.02	18	610	22	<5	<20	24	0.10	<10	57	<10	34	46
21	L21400N 5025E	5	<0.2	1.38	<5	150	<5	0.33	<1	18	55	44	3.47	<10	0.96	510	1	0.01	36	470	14	<5	<20	4	0.14	<10	51	<10	5	59
22	L21400N 5050E	5	<0.2	1.55	10	125	5	0.29	<1	19	56	46	3.58	<10	0.94	509	1	0.01	39	470	18	<5	<20	2	0.17	<10	51	<10	4	60
23	L21400N 5075E	5	0.4	0.93	<5	105	5	0.18	<1	11	35	15	3.58	<10	0.34	384	1	0.01	15	410	20	<5	<20	3	0.24	<10	58	<10	<1	53
24	L21400N 5100E	5	0.2	0.86	<5	75	<5	0.13	<1	10	30	10	2.77	<10	0.25	293	<1	0.01	12	270	16	<5	<20	1	0.21	<10	56	<10	<1	31
25	L21400N 5125E	5	0.4	1.60	5	75	15	0.18	<1	15	57	24	3.89	<10	0.67	330	3	0.01	29	270	26	<5	<20	<1	0.30	<10	62	<10	<1	59

N/	DTA	URC	CP C	FICA	FAN	IS A	14-15	OTE	ABO	JRY I																				
Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
26	L21400N 5150E	35	0.3	0.80	<5	60	10	0.16	<1	9	32	10	3.10	<10	0.29	157	2	<0.01	13	450	20	<5	<20	2	0.23	<10	44	<10	<1	34
27	L21400N 5175E	10	0.4	1.50	10	185	<5	0.70	<1	14	43	38	2.81	<10	0.61	826	2	0.01	32	630	22	<5	<20	26	0.09	<10	47	<10	24	79
28	L21400N 5200E	5	0.2	0.41	<5	65	<5	0.07	<1	4	12	7	1.79	<10	0.05	70	1	<0.01	7	210	12	<5	<20	<1	0.10	<10	43	<10	<1	21
29	L21400N 5225E	5	0.7	0.72	10	50	<5	0.04	<1	4	12	11	2.30	<10	0.07	98	2	<0.01	10	310	18	<5	<20	<1	0.05	<10	45	<10	<1	24
30	L21400N 5250E	5	<0.2	1.58	10	115	5	0.27	<1	13	46	26	3.23	<10	0.67	244	2	0.01	27	240	20	<5	<20	6	0.18	<10	42	<10	9	58
31	L21400N 5275E	45	0.2	0.66	<5	75	5	0.10	<1	8	24	10	2.93	<10	0.18	111	<1	0.01	10	210	18	<5	<20	<1	0.24	<10	49	<10	<1	32
32	L21400N 5300E	<5	<0.2	0.46	<5	50	10	0.06	<1	5	15	6	1.88	<10	0.09	112	2	0.01	6	250	16	<5	<20	<1	0.18	<10	43	<10	<1	23
33	L21400N 5325E	5	<0.2	1.69	10	110	5	0.25	<1	16	49	34	3.16	<10	0.71	371	2	0.01	32	380	20	<5	<20	1	0.14	<10	37	<10	24	65
34	L21400N 5350E	5	0.2	1.46	10	120	<5	0.36	<1	18	48	35	3.30	<10	0.76	738	3	0.01	34	400	18	<5	<20	8	0.13	<10	53	<10	15	63
35	L21400N 5375E	<5	0.2	1.73	<5	60	10	0.08	<1	8	29	29	2.70	<10	0.08	50	1	0.01	9	250	24	<5	<20	1	0.25	10	35	<10	9	19
36	L21400N 5400E	<5	0.4	1.40	5	140	5	0.28	<1	18	40	27	3.06	<10	0.48	541	2	0.01	23	360	22	<5	<20	9	0.08	<10	34	<10	19	52
37	L21400N 5425E	<5	0.7	1.60	5	180	5	0.38	<1	10	35	31	3.12	<10	0.31	431	2	0.01	18	400	22	<5	<20	8	0.09	<10	18	<10	10	49
38	L21400N 5450E	5	0.3	0.85	<5	70	10	0.13	<1	10	34	21	3.73	<10	0.17	135	3	0.01	14	170	22	<5	<20	<1	0.16	<10	30	<10	4	38
39	L21400N 5475E	<5	0.4	1.48	5	105	10	0.15	<1	14	44	30	4.74	<10	0.42	173	3	0.01	22	230	24	<5	<20	1	0.15	<10	38	<10	2	52
40	L21400N 5500E	5	0.5	1.49	5	125	10	0.25	<1	16	52	23	4.44	<10	0.74	280	3	<0.01	37	180	22	<5	<20	4	0.14	<10	50	<10	3	71
41	L21800N 4500E	25	0.3	0.99	<5	75	5	0.10	<1	6	17	14	2.14	<10	0.16	314	2	0.01	9	430	18	<5	<20	<1	0.06	<10	31	<10	9	26
42	L21800N 4525E	<5	0.3	1.19	<5	50	5	0.09	<1	6	14	18	2.06	<10	0.12	184	3	0.01	5	400	18	<5	<20	<1	0.05	<10	33	<10	7	22
43	L21800N 4550E	<5	0.5	1.38	5	65	<5	0.16	<1	6	10	45	1.44	<10	0.07	241	2	0.01	6	470	20	<5	<20	4	0.03	<10	22	<10	38	18
44	L21800N 4575E	<5	0.9	2.95	15	105	<5	0.44	<1	7	31	97	2.01	20	0.19	483	1	0.02	13	780	32	<5	<20	14	0.04	<10	26	<10	81	50
45	L21800N 4600E	<5	0.2	0.51	<5	125	<5	0.27	<1	5	13	8	1.53	<10	0.12	209	2	0.01	6	460	20	<5	<20	5	0.07	<10	24	<10	2	28
46	L21800N 4625E	<5	<0.2	0.37	<5	65	5	0.10	<1	4	17	7	1.35	<10	0.09	73	1	0.01	7	170	20	<5	<20	<1	0.05	<10	21	<10	<1	19
47	L21800N 4650E	5	<0.2	0.46	<5	170	<5	0.31	<1	10	31	9	1.96	<10	0.16	1077	2	0.01	9	320	16	<5	<20	8	0.05	<10	50	<10	<1	36
48	L21800N 4675E	<5	<0.2	0.29	<5	175	<5	0.22	<1	3	13	7	1.20	<10	0.07	238	1	0.01	6	210	14	<5	<20	6	0.05	<10	27	<10	<1	32
49	L21800N 4700E	<5	<0.2	0.66	<5	100	5	0.15	<1	7	19	12	2.38	<10	0.15	223	2	0.01	8	330	16	<5	<20	3	0.08	<10	31	<10	<1	25
50	L21800N 4725E	<5	0.4	1.04	<5	95	20	0.19	<1	10	41	13	3.21	<10	0.32	192	3	0.01	14	310	18	<5	<20	1	0.16	<10	31	<10	4	31
51	L21800N 4750E	<5	0.2	1.03	<5	70	10	0.11	<1	8	27	13	3.68	<10	0.15	340	2	0.01	8	380	20	<5	<20	1	0.12	<10	52	<10	<1	29
52	L21800N 4775E	<5	0.2	0.98	<5	140	10	0.23	<1	12	28	14	2.87	<10	0.29	367	2	0.01	12	330	18	<5	<20	8	0.10	<10	43	<10	10	30
53	L21800N 4800E	10	0.2	0.93	5	280	5	0.06	<1	8	29	37	3.61	<10	0.21	269	4	<0.01	21	340	28	<5	<20	<1	0.04	<10	35	<10	1	65
54	L21800N 4825E	<5	<0.2	1.45	<5	120	15	0.22	<1	16	54	18	3.79	<10	0.67	348	2	<0.01	25	280	20	<5	<20	2	0.16	<10	26	<10	7	47
55	L21800N 4850E	5	<0.2	1.05	<5	180	10	0.20	<1	13	42	16	3.90	<10	0.45	219	2	0.01	19	280	16	<5	<20	6	0.17	<10	27	<10	6	40
56	L21800N 4875E	<5	1.2	2.56	5	315	<5	0.49	2	25	60	82	3.67	20	0.57	1308	3	0.02	63	830	38	<5	<20	65	0.05	<10	75	<10	76	183
57	L21800N 4900E	<5	0.2	0.72	<5	150	10	0.19	<1	8	26	13	2.59	<10	0.19	152	2	0.01	13	320	18	<5	<20	12	0.10	<10	23	<10	6	53
58	L21800N 4925E	<5	0.4	1.19	<5	105	10	0.14	<1	13	39	16	3.45	<10	0.29	380	3	0.01	20	330	20	<5	<20	2	0.10	<10	41	<10	3	82
59	L21800N 4950E	<5	0.3	0.97	<5	120	10	0.12	<1	9	29	13	3.07	<10	0.23	206	3	0.01	14	390	20	<5	<20	2	0.09	<10	24	<10	3	58
60	L21800N 4975E	10	0.2	1.13	<5	80	15	0.17	<1	12	42	12	4.10	<10	0.34	191	3	0.01	16	780	20	<5	<20	<1	0.14	<10	29	<10	3	61
61	L21800N 5025E	5	0.3	0.65	<5	75	5	0.12	<1	7	26	16	2.63	<10	0.14	165	2	0.01	9	550	20	<5	<20	1	0.10	<10	41	<10	1	43
62	L21800N 5050E	<5	0.3	1.10	<5	115	10	0.16	<1	16	39	13	3.44	<10	0.32	806	3	0.01	19	420	20	<5	<20	2	0.11	<10	33	<10	3	65
63	L21800N 5075E	<5	0.4	1.80	<5	205	<5	0.21	<1	15	54	36	4.45	<10	0.44	348	4	0.01	49	470	32	<5	<20	12	0.09	<10	55	<10	1	86
64	L21800N 5100E	<5	0.4	0.64	<5	90	10	0.12	<1	8	24	10	2.80	<10	0.14	103	2	0.01	11	350	20	<5	<20	2	0.10	<10	32	<10	3	35
65	L21800N 5125E	<5	0.3	1.12	<5	115	10	0.19	<1	13	40	13	3.39	<10	0.42	544	2	0.01	18	480	24	<5	<20	2	0.11	<10	26	<10	2	61

Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
66	L21800N 5150E	<5	0.3	1.20	<5	105	5	0.18	<1	12	38	13	3.38	<10	0.35	376	2	<0.01	15	420	20	<5	<20	1	0.12	<10	29	<10	3	59
67	L21800N 5175E	<5	<0.2	1.01	<5	125	10	0.16	<1	13	40	14	3.72	<10	0.39	443	3	0.01	18	400	18	<5	<20	<1	0.12	<10	40	<10	2	51
68	L21800N 5200E	5	0.2	0.78	<5	125	10	0.12	<1	11	28	12	3.00	<10	0.17	527	2	0.01	11	360	16	<5	<20	2	0.11	<10	32	<10	3	44
69	L21800N 5225E	5	0.3	0.88	<5	140	10	0.23	<1	14	42	17	3.58	<10	0.36	604	2	0.01	15	550	18	<5	<20	3	0.11	<10	39	<10	4	54
70	L21800N 5250E	<5	1.0	1.79	<5	235	<5	0.46	<1	18	41	60	3.02	10	0.40	1958	2	0.01	32	610	26	<5	<20	32	0.06	<10	42	<10	40	73
71	L21800N 5275E	5	1.2	1.89	5	205	<5	0.43	<1	17	41	74	2.80	20	0.39	2196	2	0.02	25	610	24	<5	<20	29	0.06	<10	68	<10	59	55
72	L21800N 5300E	5	0.6	0.97	<5	370	<5	0.57	<1	12	28	41	2.63	<10	0.29	2775	2	0.01	25	630	22	<5	<20	46	0.05	<10	57	<10	26	59
73	L21800N 5325E	<5	0.4	0.42	<5	105	<5	0.13	<1	6	16	16	1.91	<10	0.13	385	1	0.01	11	410	22	<5	<20	6	0.07	<10	44	<10	<1	35
74	L21800N 5350E	35	0.2	1.61	15	145	<5	0.20	<1	21	49	44	4.67	<10	0.72	548	4	<0.01	52	580	28	<5	<20	6	0.08	<10	56	<10	<1	89
75	L21800N 5375E	5	1.7	2.59	20	580	<5	0.72	<1	32	69	138	3.94	20	0.60	4805	3	0.02	70	1420	38	<5	<20	62	0.03	<10	73	<10	88	109
76	L21800N 5400E	<5	1.9	1.42	10	540	<5	1.12	2	14	24	92	1.39	40	0.24	3368	<1	0.01	25	1000	20	<5	<20	100	0.02	<10	30	<10	103	26
77	L21800N 5425E	<5	1.4	1.65	<5	360	5	0.42	<1	14	43	46	3.65	<10	0.40	1258	4	0.02	34	510	30	<5	<20	32	0.11	<10	40	<10	25	73
78	L21800N 5450E	<5	0.5	0.28	<5	60	<5	0.07	<1	3	11	7	1.16	<10	0.04	85	<1	0.01	6	260	12	<5	<20	2	0.06	<10	35	<10	<1	19
79	L21800N 5475E	5	0.7	0.76	<5	105	<5	0.12	<1	9	28	13	3.07	<10	0.26	263	3	0.01	17	440	18	<5	<20	4	0.09	<10	58	<10	<1	45
80	L21800N 5500E	5	0.3	1.96	10	195	<5	0.23	<1	18	64	51	4.99	<10	0.81	369	4	0.01	60	360	28	<5	<20	9	0.15	<10	65	<10	<1	86

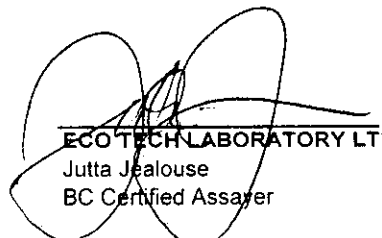
QC DATA:

Repeat:

1	L21400N 4500E	75	0.2	1.30	20	150	10	0.38	<1	24	8	25	6.81	<10	0.24	3438	5	0.02	5	970	34	<5	<20	14	0.05	<10	44	<10	2	74
2	L21400N 4525E	45																												
10	L21400N 4725E	5	<0.2	2.06	20	165	<5	0.21	<1	22	63	40	4.15	<10	0.88	652	1	0.01	39	260	22	<5	<20	2	0.14	<10	66	<10	3	56
19	L21400N 4950E	5	0.3	1.21	<5	155	5	0.12	<1	15	42	18	3.89	<10	0.46	561	2	0.01	19	380	18	<5	<20	<1	0.29	<10	63	<10	<1	53
28	L21400N 5200E	5	0.2	0.42	<5	65	5	0.07	<1	4	13	8	1.87	<10	0.05	74	2	<0.01	7	230	14	<5	<20	1	0.10	<10	42	<10	<1	22
36	L21400N 5400E	<5	0.4	1.43	5	125	5	0.28	<1	15	35	24	2.98	<10	0.47	466	2	0.01	20	310	20	<5	<20	6	0.07	<10	34	<10	17	48
38	L21400N 5450E	<5																												
45	L21800N 4600E	<5	0.2	0.51	<5	130	<5	0.28	<1	5	13	9	1.58	<10	0.12	208	1	<0.01	7	490	20	<5	<20	6	0.07	<10	25	<10	1	29
54	L21800N 4825E	5	<0.2	1.39	<5	120	10	0.20	<1	15	51	17	3.66	<10	0.64	339	3	<0.01	25	260	20	<5	<20	<1	0.16	<10	26	<10	7	46
63	L21800N 5075E	<5	0.4	1.78	<5	210	5	0.20	<1	15	53	36	4.44	<10	0.43	365	4	0.01	47	490	34	<5	<20	11	0.09	<10	58	<10	<1	87
71	L21800N 5275E	<5	1.1	1.89	<5	205	<5	0.41	<1	17	41	69	2.82	20	0.39	2205	3	0.01	26	640	24	<5	<20	30	0.07	<10	67	<10	58	55
72	L21800N 5300E	5																												
74	L21800N 5350E	65																												
80	L21800N 5500E	<5	0.3	1.88	15	180	<5	0.23	<1	18	62	46	4.76	<10	0.82	361	4	0.01	58	340	24	<5	<20	8	0.13	<10	64	<10	<1	85

Standard:

3EO'04	140	1.4	1.36	45	155	<5	1.26	<1	15	52	86	3.47	<10	0.75	550	1	0.02	28	630	22	<5	<20	49	0.10	<10	72	<10	9	69
3EO'04	135	1.5	1.48	50	145	<5	1.35	<1	17	56	84	3.79	<10	0.81	582	<1	0.02	28	640	24	<5	<20	53	0.11	<10	68	<10	9	71
3EO'04	140	1.5	1.58	50	140	<5	1.41	<1	17	59	84	3.86	<10	0.85	593	<1	0.03	26	610	26	<5	<20	61	0.11	<10	71	<10	9	70


ECO TECH LABORATORY LTD.
 Jutta Jealous
 BC Certified Assayer

ECO TECH LABORATORY LTD.
10041 Dallas Drive
KAMLOOPS, B.C.
V2C 6T4

ICP CERTIFICATE OF ANALYSIS AK 2004-1595

NAVASOTA RESOURCES
#207 141 VICTORIA STREET
KAMLOOPS, BC
V2C 1Z5

Phone: 250-573-5700
Fax : 250-573-4557

No. of samples received: 100
Sample type: Soil
Samples submitted by: Not Indicated

Values in ppm unless otherwise reported

Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zr
1	L21300N 5025E	5	0.3	1.57	5	145	5	0.36	<1	15	48	26	3.32	<10	0.60	553	<1	0.01	27	330	20	<5	<20	14	0.23	<10	37	<10	17	55
2	L21300N 5050E	<5	0.8	1.03	<5	145	5	0.13	<1	15	41	15	3.80	<10	0.28	2544	<1	0.01	13	480	16	<5	<20	5	0.31	<10	85	<10	<1	54
3	L21300N 5075E	<5	0.3	1.41	<5	95	5	0.15	<1	15	43	18	3.99	<10	0.36	763	1	0.01	16	520	22	<5	<20	6	0.22	<10	47	<10	<1	64
4	L21300N 5100E	10	0.2	1.26	<5	140	10	0.21	<1	18	46	19	4.41	<10	0.43	1311	1	0.01	22	410	18	<5	<20	7	0.23	<10	65	<10	<1	56
5	L21300N 5125E	20	0.3	0.83	30	110	<5	0.06	<1	15	22	23	3.86	<10	0.13	1150	2	0.01	28	440	20	<5	<20	5	0.07	<10	65	<10	<1	65
6	L21300N 5150E	10	0.3	0.86	15	80	10	0.14	<1	9	24	14	2.92	<10	0.18	401	1	<0.01	14	400	24	<5	<20	6	0.15	<10	47	<10	<1	44
7	L21300N 5175E	5	0.4	1.13	<5	70	5	0.17	<1	8	29	11	2.68	<10	0.27	164	1	0.01	11	230	20	<5	<20	8	0.19	<10	40	<10	1	32
8	L21300N 5200E	<5	0.2	0.99	5	85	5	0.16	<1	10	35	12	2.95	<10	0.36	178	1	<0.01	15	290	18	<5	<20	5	0.20	<10	40	<10	<1	44
9	L21300N 5225E	5	0.3	0.64	<5	85	5	0.17	<1	8	23	11	2.14	<10	0.19	277	<1	0.01	10	340	16	<5	<20	6	0.13	<10	38	<10	<1	36
10	L21300N 5250E	<5	0.3	0.82	<5	125	5	0.18	<1	9	28	10	2.96	<10	0.25	442	1	0.01	12	350	18	<5	<20	8	0.23	<10	45	<10	<1	40
11	L21300N 5275E	40	0.3	1.00	<5	60	5	0.16	<1	10	30	10	3.02	<10	0.33	389	1	0.01	13	310	18	<5	<20	4	0.24	<10	42	<10	<1	43
12	L21300N 5300E	<5	0.2	0.93	<5	60	5	0.11	<1	9	28	11	3.23	<10	0.23	154	<1	0.01	12	320	18	<5	<20	4	0.24	<10	39	<10	<1	34
13	L21300N 5325E	<5	0.3	0.66	<5	70	10	0.19	<1	9	22	12	3.04	<10	0.13	659	1	0.01	8	610	16	<5	<20	7	0.19	<10	42	<10	<1	35
14	L21300N 5350E	<5	0.3	0.45	<5	60	5	0.08	<1	4	10	6	1.68	<10	0.03	116	<1	0.01	5	390	14	<5	<20	5	0.12	<10	28	<10	<1	20
15	L21300N 5375E	<5	0.3	0.78	<5	55	10	0.05	<1	8	21	10	3.57	<10	0.09	205	2	0.01	8	260	16	<5	<20	2	0.22	<10	43	<10	<1	34
16	L21300N 5400E	5	0.3	0.80	<5	125	5	0.18	<1	24	29	26	2.53	<10	0.22	1516	1	0.01	13	330	20	<5	<20	8	0.16	<10	47	<10	4	40
17	L21300N 5425E	<5	0.3	1.35	<5	155	<5	0.19	<1	51	26	32	2.49	<10	0.21	1504	<1	0.01	13	350	20	<5	<20	11	0.17	<10	53	<10	13	39
18	L21300N 5450E	<5	0.5	1.52	<5	175	<5	0.25	<1	18	26	52	2.25	<10	0.16	3018	2	0.02	15	480	22	<5	<20	17	0.09	<10	58	<10	20	38
19	L21300N 5475E	<5	1.0	2.64	10	175	<5	0.31	<1	19	39	59	2.79	<10	0.29	2152	2	0.02	26	600	28	<5	<20	18	0.11	<10	53	<10	21	52
20	L21300N 5500E	<5	1.6	2.36	10	265	<5	0.44	<1	12	42	80	2.48	10	0.33	642	4	0.02	34	1430	28	<5	<20	31	0.03	<10	77	<10	30	58
21	L21600N 4500E	<5	0.2	0.80	<5	95	10	0.13	<1	7	19	14	3.03	<10	0.16	428	3	0.01	9	350	12	<5	<20	5	0.12	<10	46	<10	<1	43
22	L21600N 4525E	<5	0.3	1.36	20	90	5	0.15	<1	24	18	27	2.55	<10	0.17	1526	2	0.01	11	470	22	<5	<20	6	0.11	<10	39	<10	11	46
23	L21600N 4550E	<5	0.2	0.65	<5	90	10	0.08	<1	7	16	13	2.72	<10	0.15	215	2	0.01	9	290	12	<5	<20	5	0.14	<10	40	<10	<1	29
24	L21600N 4575E	<5	0.2	0.81	<5	90	5	0.13	<1	7	23	14	3.05	<10	0.17	269	2	0.01	10	500	16	<5	<20	6	0.13	<10	52	<10	<1	32
25	L21600N 4600E	<5	0.5	1.37	5	365	5	0.65	<1	12	23	23	2.24	<10	0.24	2843	2	0.01	15	820	26	<5	<20	21	0.05	<10	49	<10	19	55

N.	OTA	JUR	IC	TIFI	OF	YSIS	2004	CO T	LAB	ORY																				
Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
26	L21600N 4625E	<5	0.2	1.27	<5	170	10	0.23	<1	8	32	12	3.78	<10	0.21	206	3	0.01	9	330	22	<5	<20	12	0.18	<10	52	<10	6	47
27	L21600N 4650E	<5	<0.2	0.41	<5	95	<5	0.13	<1	4	17	9	1.62	<10	0.08	170	2	0.01	4	260	14	<5	<20	5	0.09	<10	41	<10	<1	22
28	L21600N 4675E	<5	0.4	1.50	10	215	5	0.23	<1	14	32	37	3.22	<10	0.30	1305	2	0.01	16	470	20	<5	<20	13	0.09	<10	68	<10	24	53
29	L21600N 4700E	<5	0.5	1.35	10	225	<5	1.14	<1	11	34	34	1.87	<10	0.31	1195	1	0.01	17	970	22	<5	<20	41	0.04	<10	43	<10	39	45
30	L21600N 4725E	<5	<0.2	1.22	<5	70	5	0.13	<1	10	32	15	3.62	<10	0.35	180	2	0.01	16	300	20	<5	<20	6	0.14	<10	39	<10	<1	34
31	L21600N 4750E	<5	<0.2	0.36	<5	60	10	0.09	<1	5	14	7	1.58	<10	0.08	76	<1	0.01	5	260	14	<5	<20	5	0.20	<10	39	<10	<1	20
32	L21600N 4775E	<5	0.3	1.18	<5	50	5	0.06	<1	4	19	15	1.64	<10	0.14	76	2	0.01	8	460	18	<5	<20	3	0.08	<10	30	<10	5	18
33	L21600N 4800E	<5	0.2	1.56	<5	105	10	0.22	<1	12	52	17	3.35	<10	0.57	238	3	0.01	23	240	18	<5	<20	7	0.20	<10	43	<10	1	42
34	L21600N 4825E	<5	0.2	0.60	<5	185	5	0.20	<1	8	22	12	2.32	<10	0.18	875	2	0.01	10	390	22	<5	<20	10	0.10	<10	47	<10	<1	53
35	L21600N 4850E	10	<0.2	0.89	<5	180	10	0.21	<1	8	37	13	2.68	<10	0.42	313	2	0.01	16	500	18	<5	<20	10	0.11	<10	48	<10	<1	64
36	L21600N 4875E	5	0.2	0.25	<5	125	<5	0.14	<1	3	12	7	1.05	<10	0.03	48	<1	0.01	6	250	14	<5	<20	10	0.06	<10	40	<10	<1	23
37	L21600N 4900E	5	0.8	1.94	10	145	10	0.17	<1	12	49	23	4.22	<10	0.47	233	3	0.01	23	560	22	<5	<20	7	0.16	<10	46	<10	<1	72
38	L21600N 4925E	<5	0.6	0.64	<5	85	10	0.15	<1	8	30	13	2.70	<10	0.21	292	2	0.01	10	610	16	<5	<20	4	0.17	<10	43	<10	<1	32
39	L21600N 4950E	<5	0.3	0.68	<5	115	5	0.23	<1	9	32	18	2.73	<10	0.22	471	2	0.01	13	360	14	<5	<20	8	0.16	<10	70	<10	<1	45
40	L21600N 4975E	<5	0.2	0.59	<5	70	5	0.12	<1	6	22	8	2.11	<10	0.18	156	1	0.01	7	270	16	<5	<20	4	0.18	<10	32	<10	<1	25
41	L21600N 5025E	15	0.3	0.25	<5	35	<5	0.02	<1	3	6	12	1.85	<10	0.01	65	3	0.01	12	360	14	<5	<20	3	<0.01	<10	47	<10	<1	37
42	L21600N 5050E	<5	0.3	0.52	<5	85	5	0.08	<1	3	15	9	1.76	<10	0.07	134	2	0.01	5	490	16	<5	<20	5	0.06	<10	40	<10	<1	23
43	L21600N 5075E	<5	0.3	0.58	<5	105	<5	0.09	<1	5	20	12	2.08	<10	0.12	249	2	0.01	8	370	14	<5	<20	7	0.08	<10	62	<10	<1	24
44	L21600N 5100E	<5	<0.2	0.62	<5	95	5	0.13	<1	9	31	12	2.63	<10	0.24	191	2	0.01	13	450	14	<5	<20	5	0.15	<10	56	<10	<1	35
45	L21600N 5125E	<5	0.2	0.65	<5	165	5	0.12	<1	9	25	10	2.24	<10	0.22	994	1	0.01	12	520	14	<5	<20	5	0.14	<10	50	<10	1	34
46	L21600N 5150E	<5	0.3	0.55	<5	100	5	0.13	<1	6	19	11	1.75	<10	0.15	526	2	0.01	8	500	24	<5	<20	6	0.10	<10	29	<10	1	32
47	L21600N 5175E	<5	<0.2	0.32	<5	70	<5	0.10	<1	4	15	7	1.06	<10	0.08	114	<1	0.01	5	240	16	<5	<20	5	0.16	<10	22	<10	2	19
48	L21600N 5200E	5	0.6	0.65	<5	80	<5	0.10	<1	7	21	12	2.55	<10	0.14	280	2	0.02	9	390	16	<5	<20	6	0.13	<10	49	<10	<1	35
49	L21600N 5225E	5	0.4	0.88	5	125	5	0.25	<1	10	40	20	2.91	<10	0.37	255	2	0.01	19	290	20	<5	<20	8	0.18	<10	60	<10	<1	46
50	L21600N 5250E	5	0.2	1.56	10	290	<5	0.52	<1	18	49	41	2.83	<10	0.58	1349	2	0.02	30	630	28	<5	<20	26	0.10	<10	58	<10	29	95
51	L21600N 5275E	<5	0.3	1.59	10	140	<5	0.23	<1	16	55	46	3.59	<10	0.56	445	2	0.01	27	410	24	<5	<20	9	0.15	<10	52	<10	9	70
52	L21600N 5300E	5	0.3	1.59	10	185	<5	0.39	<1	16	48	37	2.98	<10	0.54	892	2	0.01	27	560	20	<5	<20	21	0.11	<10	62	<10	24	75
53	L21600N 5325E	5	0.3	0.71	<5	215	<5	0.18	<1	8	30	13	2.77	<10	0.26	274	2	0.01	16	280	14	<5	<20	11	0.14	<10	59	<10	<1	49
54	L21600N 5350E	5	0.3	2.08	15	305	<5	0.67	<1	15	49	59	2.54	10	0.51	950	2	0.01	34	810	30	<5	<20	42	0.09	<10	48	<10	65	96
55	L21600N 5375E	5	0.2	1.78	10	220	<5	0.43	<1	16	51	46	3.03	<10	0.68	1034	1	0.01	34	510	26	<5	<20	20	0.16	<10	45	<10	41	79
56	L21600N 5400E	<5	0.6	1.60	10	180	<5	0.60	<1	14	44	41	2.67	<10	0.48	512	2	0.02	25	550	22	<5	<20	31	0.09	<10	55	<10	38	62
57	L21600N 5425E	5	<0.2	1.76	15	200	5	0.49	<1	20	56	52	3.51	<10	0.72	733	1	0.02	38	540	24	<5	<20	20	0.19	<10	44	<10	18	73
58	L21600N 5450E	<5	<0.2	1.57	5	135	<5	0.48	<1	18	57	35	3.42	<10	0.97	563	<1	0.01	36	410	16	<5	<20	14	0.24	<10	35	<10	13	74
59	L21600N 5475E	<5	0.4	1.34	10	175	<5	0.37	<1	11	44	26	2.81	<10	0.55	263	1	0.01	24	330	20	<5	<20	18	0.19	<10	42	<10	10	51
60	L21600N 5500E	15	0.2	1.40	40	120	<5	0.03	<1	16	37	44	5.28	<10	0.40	300	4	<0.01	69	330	30	<5	<20	5	0.01	<10	48	<10	<1	118
61	L22000N 4500E	<5	0.3	0.79	<5	80	<5	0.16	<1	6	22	16	2.42	<10	0.18	228	2	0.02	10	440	14	<5	<20	7	0.16	<10	56	<10	<1	27
62	L22000N 4525E	<5	1.5	1.92	35	155	<5	0.48	<1	8	68	63	2.19	<10	0.27	477	2	0.02	25	1100	28	<5	<20	18	0.03	<10	76	<10	70	48
63	L22000N 4550E	<5	0.2	1.17	<5	65	<5	0.12	<1	5	14	11	1.76	<10	0.08	102	<1	0.02	5	300	20	<5	<20	7	0.15	<10	23	<10	5	20
64	L22000N 4575E	<5	0.5	2.03	35	80	<5	0.44	<1	5	25	40	1.49	<10	0.13	689	2	0.02	10	950	20	<5	<20	14	0.05	<10	48	<10	19	30
65	L22000N 4600E	<5	0.8	0.97	10	230	<5	0.79	<1	11	33	45	1.58	<10	0.13	272	2	0.03	14	970	18	<5	<20	37	0.03	<10	36	<10	37	16

Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Z
66	L22000N 4625E	<5	1.2	3.04	20	330	<5	0.59	<1	15	73	80	3.45	10	0.58	503	2	0.02	46	680	32	<5	<20	36	0.15	<10	87	<10	64	7
67	L22000N 4650E	5	0.6	1.08	<5	105	5	0.15	<1	9	21	21	2.54	<10	0.15	114	1	0.02	9	250	18	<5	<20	9	0.21	<10	36	<10	13	3
68	L22000N 4675E	<5	0.2	0.65	<5	115	5	0.13	<1	7	24	14	2.41	<10	0.15	177	<1	0.01	10	370	16	<5	<20	7	0.19	<10	62	<10	<1	2
69	L22000N 4700E	<5	0.4	1.39	5	385	<5	0.43	<1	13	41	38	3.05	<10	0.35	553	2	0.02	23	510	24	<5	<20	23	0.17	<10	73	<10	25	5
70	L22000N 4725E	<5	0.2	0.78	<5	150	5	0.24	<1	8	29	12	2.97	<10	0.21	274	1	0.01	13	350	16	<5	<20	8	0.27	<10	76	<10	<1	4
71	L22000N 4750E	25	0.2	1.07	<5	135	5	0.20	<1	13	42	16	3.22	<10	0.38	802	1	0.01	19	380	16	<5	<20	9	0.24	<10	67	<10	<1	5
72	L22000N 4775E	5	0.2	1.18	<5	155	10	0.46	<1	10	37	18	3.32	<10	0.35	192	1	0.01	18	330	22	<5	<20	27	0.26	<10	78	<10	5	4
73	L22000N 4800E	<5	0.3	1.39	<5	160	5	0.26	<1	13	44	27	3.41	<10	0.42	351	1	0.01	25	430	24	<5	<20	23	0.21	<10	79	<10	15	6
74	L22000N 4825E	5	0.3	2.02	5	105	<5	0.31	<1	18	64	28	3.68	<10	0.85	342	3	0.01	44	270	22	<5	<20	7	0.30	<10	67	<10	7	8
75	L22000N 4850E	<5	0.8	1.88	5	75	<5	0.16	<1	12	44	30	3.09	<10	0.41	257	2	0.01	29	300	24	<5	<20	7	0.23	<10	50	<10	9	10
76	L22000N 4875E	5	0.3	1.25	<5	150	5	0.21	<1	11	45	15	3.51	<10	0.42	373	2	0.01	23	340	22	<5	<20	11	0.29	<10	72	<10	<1	12
77	L22000N 4900E	5	0.4	2.06	5	100	5	0.22	1	16	59	26	3.66	<10	0.68	311	3	0.01	51	310	24	<5	<20	6	0.29	<10	72	<10	5	21
78	L22000N 4925E	5	0.5	1.44	<5	75	10	0.13	1	26	37	30	3.18	<10	0.24	748	1	0.01	39	290	20	<5	<20	8	0.26	<10	60	<10	16	14
79	L22000N 4950E	5	0.5	1.87	20	120	5	0.33	<1	21	56	26	4.07	<10	0.62	995	1	0.01	92	390	24	<5	<20	33	0.20	<10	67	<10	7	26
80	L22000N 4975E	5	0.2	2.32	5	130	5	0.24	<1	18	73	31	4.28	<10	0.75	354	<1	0.01	49	280	24	<5	<20	8	0.39	<10	76	<10	4	16
81	L22200N 4500E	<5	0.2	0.50	<5	60	<5	0.07	<1	4	16	9	1.71	<10	0.07	68	<1	0.01	6	330	16	<5	<20	3	0.37	<10	61	<10	<1	17
82	L22200N 4525E	<5	0.2	0.76	<5	70	5	0.11	<1	6	23	9	2.63	<10	0.16	123	<1	0.01	7	410	20	<5	<20	5	1.11	<10	76	<10	<1	24
83	L22200N 4550E	5	<0.2	0.51	<5	50	<5	0.08	<1	4	18	8	1.49	<10	0.10	65	<1	0.01	6	260	14	<5	<20	3	0.23	<10	44	<10	2	15
84	L22200N 4575E	5	<0.2	0.74	<5	55	<5	0.08	<1	5	18	9	2.15	<10	0.11	85	<1	0.01	7	240	18	<5	<20	4	0.27	<10	45	<10	<1	17
85	L22200N 4600E	<5	0.3	0.90	5	125	5	0.11	<1	6	26	17	2.54	<10	0.18	228	2	0.01	13	460	20	<5	<20	7	0.14	<10	66	<10	<1	38
86	L22200N 4625E	<5	1.2	0.97	5	105	5	0.16	<1	6	34	16	2.89	<10	0.26	232	<1	<0.01	16	430	24	<5	<20	5	0.18	<10	62	<10	<1	44
87	L22200N 4650E	<5	0.2	1.25	10	90	15	0.21	<1	12	47	16	3.31	<10	0.49	251	<1	0.01	20	330	26	<5	<20	2	0.25	<10	60	<10	7	47
88	L22200N 4675E	<5	0.4	1.45	<5	90	<5	0.13	<1	9	41	21	3.11	<10	0.36	220	2	0.01	18	390	24	<5	<20	5	0.19	<10	65	<10	<1	37
89	L22200N 4700E	<5	<0.2	0.67	<5	70	5	0.12	<1	7	20	12	2.39	<10	0.16	140	1	0.01	10	250	16	<5	<20	5	0.19	<10	42	<10	<1	28
90	L22200N 4725E	<5	0.3	1.08	<5	180	10	0.20	<1	14	35	21	2.87	<10	0.31	592	1	0.01	19	270	20	<5	<20	15	0.20	<10	58	<10	3	49
91	L22200N 4750E	5	0.2	1.00	<5	170	5	0.30	<1	10	41	14	2.95	<10	0.38	305	1	0.01	18	270	16	<5	<20	13	0.30	<10	67	<10	1	40
92	L22200N 4775E	<5	1.1	2.06	5	235	<5	1.23	<1	8	46	35	2.37	<10	0.41	553	<1	0.02	24	870	22	<5	<20	69	0.07	<10	62	<10	22	85
93	L22200N 4800E	<5	0.5	1.11	<5	95	5	0.33	<1	10	27	21	2.25	<10	0.28	173	<1	0.02	13	290	20	<5	<20	23	0.18	<10	36	<10	11	32
94	L22200N 4825E	<5	0.8	1.84	5	130	<5	0.34	<1	26	42	28	2.64	<10	0.48	763	<1	0.02	25	470	24	<5	<20	24	0.18	<10	70	<10	18	50
95	L22200N 4850E	<5	0.3	1.88	5	85	10	0.24	<1	17	65	22	3.88	<10	0.67	300	<1	0.01	29	350	22	<5	<20	7	0.44	<10	48	<10	5	64
96	L22200N 4875E	<5	1.4	1.56	<5	85	<5	0.14	<1	12	38	23	2.82	<10	0.34	297	1	0.01	21	410	20	<5	<20	7	0.21	<10	69	<10	6	43
97	L22200N 4900E	<5	0.6	1.08	<5	70	5	0.16	<1	9	34	18	2.35	<10	0.32	140	<1	0.01	17	440	20	<5	<20	9	0.20	<10	52	<10	3	38
98	L22200N 4925E	<5	0.2	0.52	<5	40	<5	0.09	<1	6	19	7	1.98	<10	0.10	79	<1	0.01	5	260	14	<5	<20	4	0.33	<10	48	<10	<1	20
99	L22200N 4950E	<5	0.8	1.23	<5	65	<5	0.11	<1	5	21	18	1.03	10	0.14	51	<1	0.01	12	430	18	<5	<20	7	0.15	<10	25	<10	21	18
100	L22200N 4975E	<5	0.3	0.82	<5	65	10	0.15	<1	9	31	11	2.63	<10	0.25	123	<1	0.01	12	320	18	<5	<20	6	0.30	<10	40	<10	1	31

Et #. Tag # Au(ppb) Ag Al % As Ba Bi Ca % Cd Co Cr Cu Fe % La Mg % Mn Mo Na % NI P Pb Sb Sn Sr TI % U V W Y Z

QC DATA:

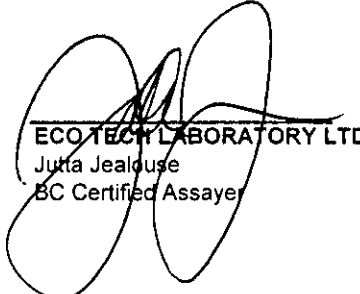
Repeat:

1	L21300N 5025E	5	0.3	1.45	<5	130	5	0.33	<1	14	44	24	3.08	<10	0.55	539	1	<0.01	24	290	18	<5	<20	12	0.18	<10	38	<10	14	5
10	L21300N 5250E	<5	0.2	0.77	<5	125	5	0.17	<1	9	27	10	2.88	<10	0.24	503	2	0.01	11	330	18	<5	<20	6	0.21	<10	45	<10	<1	4
19	L21300N 5475E	<5	1.0	2.62	10	175	5	0.32	<1	19	39	58	2.76	<10	0.29	2132	3	0.02	25	570	32	<5	<20	19	0.10	<10	50	<10	21	5
28	L21600N 4675E	5	0.3	1.39	10	205	<5	0.20	<1	13	32	33	3.05	<10	0.32	1152	2	0.01	16	430	20	<5	<20	11	0.08	<10	65	<10	21	5
30	L21600N 4725E	<5																												
36	L21600N 4875E	<5	0.2	0.23	<5	115	<5	0.13	<1	3	11	7	0.99	<10	0.03	44	<1	0.01	6	230	12	<5	<20	9	0.05	<10	40	<10	<1	2
45	L21600N 5125E	<5	0.2	0.62	<5	170	5	0.10	<1	8	24	10	2.15	<10	0.20	983	<1	0.01	11	500	14	<5	<20	3	0.14	<10	53	<10	<1	3
54	L21600N 5350E	<5	0.3	2.03	15	290	<5	0.66	<1	14	49	58	2.52	10	0.51	927	2	0.01	34	780	28	<5	<20	42	0.07	<10	50	<10	63	9
63	L22000N 4550E	75	0.2	1.14	<5	65	<5	0.11	<1	4	13	10	1.73	<10	0.07	92	<1	0.02	5	290	20	<5	<20	7	0.13	<10	24	<10	4	1
71	L22000N 4750E	<5	0.2	1.10	<5	135	5	0.20	<1	14	43	17	3.22	<10	0.38	821	1	0.01	19	410	18	<5	<20	8	0.27	<10	78	<10	<1	5
80	L22000N 4975E	5	0.2	2.34	10	130	10	0.24	<1	19	73	32	4.31	<10	0.75	347	1	0.01	51	280	26	<5	<20	7	0.34	<10	67	<10	4	16
98	L22200N 4925E	<5	0.2	0.53	<5	50	5	0.11	<1	7	22	8	2.32	<10	0.12	99	<1	0.01	7	310	16	<5	<20	4	0.32	<10	46	<10	<1	2

Standard:

GEO'04	140	1.6	1.41	50	135	<5	1.36	<1	16	55	84	3.56	<10	0.76	562	<1	0.02	25	550	22	<5	<20	55	0.11	<10	68	<10	10	7
GEO'04	135	1.6	1.52	55	145	<5	1.35	<1	16	58	86	3.76	<10	0.80	581	<1	0.02	27	590	22	<5	<20	58	0.11	<10	69	<10	9	7
GEO'04	140	1.6	1.49	55	135	<5	1.34	<1	16	57	87	3.71	<10	0.79	571	<1	0.02	26	600	24	<5	<20	57	0.11	<10	68	<10	9	7

JJ/kk
dt/
XLS/04


ECO TECH LABORATORY LTD.
 Jutta Jealous
 BC Certified Assayer

ECO TECH LABORATORY LTD.
10041 Dallas Drive
KAMLOOPS, B.C.
V2C 6T4

ICP CERTIFICATE OF ANALYSIS AK 2004-1596

NAVASOTA RESOURCES
#207 141 VICTORIA STREET
KAMLOOPS, BC
V2C 1Z5

Phone: 250-573-5700

Fax : 250-573-4557

No. of samples received: 80

Sample type: Soil

Samples submitted by: Not Indicated

Values in ppm unless otherwise reported

Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Tl %	U	V	W	Y	Zn
1	L22400N 4500E	<5	<0.2	0.64	<5	55	<5	0.09	<1	5	20	11	2.27	<10	0.09	95	1	<0.01	9	200	20	<5	<20	5	0.10	<10	42	<10	<1	23
2	L22400N 4525E	<5	<0.2	0.58	<5	65	<5	0.11	<1	7	25	9	2.58	<10	0.15	78	1	<0.01	11	210	22	<5	<20	2	0.16	<10	50	<10	<1	26
3	L22400N 4550E	<5	0.2	0.64	<5	95	<5	0.16	<1	4	20	15	1.76	<10	0.09	54	1	<0.01	11	360	20	<5	<20	4	0.05	<10	38	<10	<1	25
4	L22400N 4575E	5	<0.2	1.16	<5	60	<5	0.10	<1	10	43	19	3.48	<10	0.33	162	2	<0.01	22	330	30	<5	<20	1	0.13	<10	51	<10	<1	46
5	L22400N 4600E	<5	<0.2	0.53	<5	40	<5	0.07	<1	7	24	10	2.75	<10	0.14	171	1	<0.01	11	260	22	<5	<20	<1	0.16	<10	52	<10	<1	31
6	L22400N 4625E	<5	0.2	0.95	<5	90	<5	0.17	<1	8	30	14	3.06	<10	0.21	891	2	<0.01	14	480	22	<5	<20	5	0.11	<10	54	<10	<1	45
7	L22400N 4650E	5	0.3	1.34	<5	130	5	0.10	<1	15	43	20	3.50	<10	0.40	613	2	0.01	24	310	26	<5	<20	2	0.11	<10	54	<10	<1	89
8	L22400N 4675E	<5	1.1	2.55	15	295	<5	0.23	<1	8	46	55	2.73	<10	0.32	228	2	0.01	31	960	38	<5	<20	11	0.03	<10	66	<10	29	54
9	L22400N 4700E	<5	0.4	1.73	<5	165	<5	0.47	<1	13	66	32	3.06	<10	0.71	284	<1	0.01	36	350	26	<5	<20	21	0.09	<10	59	<10	12	47
10	L22400N 4725E	<5	0.6	1.74	<5	130	5	0.32	<1	16	54	27	2.90	<10	0.53	1049	1	0.01	28	450	30	<5	<20	13	0.06	<10	64	<10	9	62
11	L22400N 4750E	10	0.4	1.28	<5	90	<5	0.18	<1	11	43	15	3.16	<10	0.37	190	2	<0.01	20	240	24	<5	<20	4	0.13	<10	49	<10	2	43
12	L22400N 4775E	5	0.3	2.06	10	135	5	0.25	<1	16	53	20	3.78	<10	0.45	298	2	0.01	26	300	36	<5	<20	6	0.14	<10	54	<10	11	63
13	L22400N 4800E	<5	0.4	1.36	<5	145	<5	0.30	<1	14	42	18	3.06	<10	0.42	514	2	0.01	22	380	24	<5	<20	13	0.08	<10	57	<10	9	57
14	L22400N 4825E	<5	<0.2	0.89	<5	130	5	0.13	<1	10	35	12	3.63	<10	0.25	221	2	0.01	16	290	24	<5	<20	3	0.17	<10	44	<10	<1	50
15	L22400N 4850E	<5	<0.2	0.76	<5	90	<5	0.21	<1	9	35	9	3.08	<10	0.27	178	1	<0.01	15	250	20	<5	<20	6	0.15	<10	46	<10	<1	40
16	L22400N 4875E	5	0.2	1.14	<5	100	5	0.13	<1	11	38	12	3.36	<10	0.33	318	1	<0.01	18	300	24	<5	<20	2	0.16	<10	43	<10	<1	47
17	L22400N 4900E	<5	0.5	1.54	<5	80	<5	0.11	<1	11	47	24	3.28	<10	0.37	272	2	<0.01	22	620	28	<5	<20	3	0.12	<10	60	<10	<1	45
18	L22400N 4925E	<5	0.2	0.86	<5	115	<5	0.30	<1	10	36	10	2.75	<10	0.31	759	1	0.01	16	530	20	<5	<20	10	0.12	<10	39	<10	<1	59
19	L22400N 4950E	<5	0.2	0.80	<5	65	<5	0.21	<1	9	36	10	2.90	<10	0.27	411	2	<0.01	15	400	20	<5	<20	4	0.12	<10	43	<10	<1	37
20	L22400N 4975E	<5	0.3	1.00	<5	150	5	0.24	<1	12	48	12	3.67	<10	0.42	795	2	<0.01	20	300	22	<5	<20	7	0.13	<10	48	<10	<1	66
21	L22800N 4500E	<5	<0.2	1.82	5	65	<5	0.14	<1	12	57	19	3.51	<10	0.47	218	2	<0.01	26	300	28	<5	<20	1	0.13	<10	46	<10	<1	51
22	L22800N 4525E	<5	0.3	1.62	<5	85	<5	0.11	<1	10	39	21	3.05	<10	0.32	265	3	<0.01	19	320	28	<5	<20	2	0.10	<10	57	<10	4	45
23	L22800N 4550E	<5	0.4	1.59	<5	120	<5	0.24	<1	22	42	18	2.79	<10	0.38	985	2	0.01	20	410	28	<5	<20	5	0.06	<10	65	<10	7	48
24	L22800N 4575E	<5	0.2	0.95	<5	80	<5	0.16	<1	10	26	11	2.37	<10	0.20	339	2	<0.01	12	290	22	<5	<20	4	0.07	<10	56	<10	<1	31
25	L22800N 4600E	<5	0.2	2.57	<5	100	<5	0.11	<1	15	55	29	3.63	<10	0.43	465	3	0.01	24	390	40	<5	<20	3	0.10	<10	63	<10	7	64
26	L22800N 4625E	<5	0.2	1.30	<5	75	5	0.16	<1	10	41	15	3.38	<10	0.34	302	2	<0.01	17	440	30	<5	<20	3	0.11	<10	46	<10	<1	59
27	L22800N 4650E	<5	<0.2	2.43	5	80	<5	0.13	<1	12	59	20	3.79	<10	0.45	344	2	<0.01	23	330	34	<5	<20	2	0.14	<10	47	<10	<1	50
28	L22800N 4675E	<5	0.5	0.24	<5	210	<5	1.09	<1	<1	2	8	0.50	<10	0.06	12	<1	0.03	4	1080	12	<5	<20	35	<0.01	<10	3	<10	12	5
29	L22800N 4700E	<5	0.2	0.13	<5	215	<5	2.20	<1	<1	3	13	0.22	<10	0.09	61	<1	0.02	4	810	20	<5	<20	61	<0.01	<10	5	<10	10	11
30	L22800N 4725E	<5	0.2	0.72	<5	60	<5	0.08	<1	5	18	11	2.59	<10	0.03	40	2	0.01	7	240	26	<5	<20	3	0.11	<10	36	<10	<1	17

Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
31	L22800N 4750E	<5	0.3	1.85	15	100	<5	0.07	<1	7	40	17	2.98	<10	0.20	87	3	<0.01	19	370	30	<5	<20	3	0.07	<10	34	<10	<1	38
32	L22800N 4775E	<5	0.5	1.89	5	130	<5	0.47	<1	20	36	32	2.65	<10	0.24	660	3	0.01	20	480	34	<5	<20	14	0.06	<10	57	<10	22	49
33	L22800N 4800E	<5	0.4	1.14	<5	80	5	0.22	<1	11	26	16	2.68	<10	0.19	242	2	0.01	12	270	40	<5	<20	<1	0.12	<10	35	<10	9	37
34	L22800N 4825E	5	<0.2	2.03	5	80	<5	0.19	<1	19	67	29	4.06	<10	0.69	416	3	<0.01	37	270	32	<5	<20	3	0.14	<10	55	<10	1	62
35	L22800N 4850E	<5	<0.2	2.21	5	80	<5	0.21	<1	21	72	31	4.04	<10	0.80	439	3	0.01	41	250	34	<5	<20	3	0.15	<10	59	<10	2	65
36	L22800N 4875E	<5	<0.2	1.06	<5	40	5	0.10	<1	8	34	11	3.39	<10	0.19	187	2	<0.01	14	310	28	<5	<20	2	0.14	<10	50	<10	<1	37
37	L22800N 4900E	<5	<0.2	1.50	<5	60	5	0.14	<1	11	40	16	3.04	<10	0.33	339	3	0.01	19	300	28	<5	<20	3	0.11	<10	57	<10	<1	43
38	L22800N 4925E	<5	<0.2	2.28	5	80	<5	0.14	<1	17	57	21	3.75	<10	0.46	594	1	0.01	25	360	38	<5	<20	3	0.15	<10	43	<10	1	69
39	L22800N 4950E	<5	0.5	3.12	15	265	<5	0.61	<1	22	76	53	4.73	<10	0.62	680	3	0.01	49	450	48	<5	<20	32	0.11	<10	78	<10	12	134
40	L22800N 4975E	<5	0.7	2.99	20	285	<5	1.05	<1	21	94	98	4.36	<10	0.90	1182	3	0.02	74	890	46	<5	<20	85	0.07	<10	95	<10	34	125
41	L22600N 4500E	<5	<0.2	2.19	10	65	<5	0.11	<1	11	49	22	3.52	<10	0.42	203	4	<0.01	25	350	34	<5	<20	<1	0.12	<10	49	<10	2	48
42	L22600N 4525E	5	0.4	1.53	<5	85	<5	0.14	<1	11	33	33	2.18	<10	0.30	210	2	0.01	19	450	28	<5	<20	5	0.06	<10	42	<10	6	38
43	L22600N 4550E	<5	0.3	2.08	<5	145	5	0.19	<1	28	58	35	3.74	<10	0.58	664	2	0.01	34	380	38	<5	<20	2	0.10	<10	71	<10	9	75
44	L22600N 4575E	<5	0.4	1.64	5	115	<5	0.41	<1	20	36	28	2.58	<10	0.32	806	2	0.01	20	570	34	<5	<20	3	0.04	<10	67	<10	13	42
45	L22600N 4600E	<5	<0.2	1.21	10	55	<5	0.11	<1	7	35	12	3.58	<10	0.20	184	<1	0.01	11	270	28	<5	<20	13	0.16	<10	36	<10	<1	39
46	L22600N 4625E	<5	0.3	2.44	10	245	<5	0.39	<1	17	65	28	4.25	<10	0.62	573	3	0.02	35	390	32	<5	<20	15	0.20	<10	90	<10	<1	84
47	L22600N 4650E	<5	<0.2	1.34	<5	85	10	0.19	<1	11	39	18	3.13	<10	0.33	279	<1	0.01	16	230	20	<5	<20	6	0.21	<10	73	<10	2	38
48	L22600N 4675E	<5	0.2	0.29	<5	80	<5	0.18	<1	4	15	5	1.19	<10	0.06	119	<1	<0.01	6	190	20	<5	<20	5	0.13	<10	22	<10	<1	25
49	L22600N 4700E	<5	<0.2	0.88	<5	50	10	0.11	<1	9	38	12	3.74	<10	0.27	194	3	<0.01	17	630	26	<5	<20	<1	0.14	<10	71	<10	<1	37
50	L22600N 4725E	<5	0.3	0.87	<5	85	<5	0.17	<1	10	41	13	2.81	<10	0.34	468	2	<0.01	18	400	20	<5	<20	3	0.11	<10	58	<10	<1	40
51	L22600N 4750E	<5	0.6	2.11	10	160	<5	0.26	<1	29	51	49	3.20	<10	0.41	629	2	0.01	30	640	36	<5	<20	8	0.05	<10	73	<10	13	68
52	L22600N 4775E	10	<0.2	1.54	5	130	<5	0.18	<1	14	55	25	3.41	<10	0.52	291	4	<0.01	32	330	26	<5	<20	5	0.07	<10	66	<10	2	57
53	L22600N 4800E	5	<0.2	2.12	10	155	<5	0.23	<1	22	74	33	4.10	<10	0.83	429	3	0.01	45	250	34	<5	<20	5	0.11	<10	64	<10	4	76
54	L22600N 4825E	<5	<0.2	1.94	5	200	<5	0.32	<1	19	64	28	3.88	<10	0.79	521	2	<0.01	41	260	28	<5	<20	13	0.10	<10	61	<10	<1	71
55	L22600N 4850E	5	<0.2	1.39	<5	165	5	0.23	<1	17	52	20	3.57	<10	0.55	452	2	0.01	25	230	26	<5	<20	7	0.12	<10	49	<10	<1	54
56	L22600N 4875E	<5	0.2	1.19	<5	125	5	0.19	<1	14	39	15	2.90	<10	0.39	509	2	0.01	18	200	26	<5	<20	7	0.11	<10	51	<10	<1	46
57	L22600N 4900E	<5	0.6	3.22	15	280	<5	0.87	<1	26	75	59	4.15	<10	0.65	1083	4	0.01	50	660	46	<5	<20	41	0.06	<10	88	<10	32	91
58	L22600N 4925E	<5	<0.2	2.17	5	115	<5	0.19	<1	17	72	30	4.99	<10	0.74	344	4	0.01	39	300	32	<5	<20	2	0.17	<10	67	<10	<1	81
59	L22600N 4950E	15	<0.2	0.96	<5	75	10	0.12	<1	9	33	12	2.71	<10	0.27	333	1	0.01	15	220	22	<5	<20	2	0.12	<10	47	<10	<1	39
60	L22600N 4975E	5	<0.2	1.80	<5	60	5	0.16	<1	13	55	15	4.23	<10	0.45	370	3	0.01	22	340	34	<5	<20	<1	0.15	<10	64	<10	<1	56
61	L23000N 4500E	<5	<0.2	0.97	<5	25	10	0.14	<1	6	14	16	1.82	<10	0.15	133	<1	0.01	8	410	24	<5	<20	<1	0.05	<10	30	<10	<1	37
62	L23000N 4525E	<5	0.5	2.01	15	105	<5	0.30	<1	8	28	22	3.03	<10	0.19	137	3	0.01	17	410	36	<5	<20	6	0.05	<10	45	<10	7	43
63	L23000N 4550E	<5	0.3	0.77	<5	155	<5	0.29	<1	6	14	12	1.51	<10	0.08	217	2	0.02	8	290	22	<5	<20	6	0.07	<10	29	<10	2	30
64	L23000N 4575E	<5	0.3	0.96	<5	180	<5	0.22	<1	4	13	13	1.52	<10	0.07	55	2	0.01	8	280	22	<5	<20	6	0.04	<10	30	<10	6	19
65	L23000N 4600E	<5	<0.2	1.70	5	150	10	0.16	<1	13	54	19	3.65	<10	0.56	283	6	<0.01	31	270	32	5	<20	<1	0.13	<10	69	<10	<1	65
66	L23000N 4625E	<5	0.2	1.73	10	190	<5	0.25	<1	17	64	27	3.74	<10	0.75	460	<1	0.01	34	360	22	<5	<20	5	0.25	<10	79	<10	<1	63
67	L23000N 4650E	<5	<0.2	2.20	10	140	<5	0.24	<1	21	73	37	4.26	<10	0.89	429	<1	0.01	44	330	26	<5	<20	3	0.29	<10	73	<10	<1	62
68	L23000N 4675E	<5	0.2	0.80	<5	155	<5	0.31	<1	8	35	13	1.78	<10	0.36	250	<1	0.01	18	370	18	<5	<20	11	0.15	<10	43	<10	<1	41
69	L23000N 4700E	<5	<0.2	2.08	20	185	5	0.52	<1	24	75	33	4.23	<10	0.86	1272	1	0.01	39	490	24	<5	<20	15	0.19	<10	80	<10	7	83
70	L23000N 4725E	<5	0.7	3.56	55	380	<5	0.68	<1	39	86	67	5.48	10	0.51	4782	4	0.02	52	1290	40	<5	<20	28	0.06	<10	109	<10	57	104
71	L23000N 4750E	<5	<0.2	0.82	<5	190	<5	0.34	<1	12	40	15	3.26	<10	0.36	278	<1	0.01	17	160	14	<5	<20	10	0.26	<10	78	<10	<1	41
72	L23000N 4775E	5	0.8	2.51	20	210	<5	0.48	<1	15	43	28	3.60	<10	0.31	525	2	0.02	25	490	36	<5	<20	19	0.13	<10	56	<10	2	93
73	L23000N 4800E	<5	0.7	2.80	10	230	<5	0.67	<1	24	68	47	4.11	<10	0.63	1944	3	0.01	41	660	32	<5	<20	18	0.10	<10	88	<10	21	118
74	L23000N 4825E	<5	0.3	1.12	10	160	<5	1.02	<1	10	30	14	2.41	<10	0.30	417	2	0.01	17	420	18	<5	<20	22	0.10	<10	53	<10	<1	44
75	L23000N 4850E	<5	0.2	0.83	<5	115	<5	0.16	<1	8	26	14	3.24	<10	0.15	214	2	0.01	11	320	20	<5	<20	4	0.14	<10	63	<10	<1	33

Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
76	L23000N 4875E	<5	0.3	1.84	5	160	5	0.64	<1	18	42	25	3.56	<10	0.36	1085	2	0.02	24	580	30	<5	<20	16	0.12	<10	65	<10	4	76
77	L23000N 4900E	<5	0.9	1.56	<5	140	<5	0.38	<1	8	29	55	2.32	<10	0.25	327	2	0.02	22	600	26	<5	<20	15	0.05	<10	60	<10	8	36
78	L23000N 4925E	<5	0.5	0.81	<5	230	<5	0.35	<1	17	12	24	2.20	<10	0.10	814	2	0.01	11	820	30	<5	<20	23	0.02	<10	44	<10	<1	46
79	L23000N 4950E	<5	0.2	0.37	<5	200	<5	0.27	<1	3	11	13	1.38	<10	0.09	124	<1	0.01	8	360	16	<5	<20	13	0.06	<10	39	<10	<1	28
80	L23000N 4975E	<5	0.6	2.17	15	360	<5	1.14	<1	10	18	33	2.01	<10	0.22	1631	1	0.02	16	1060	26	<5	<20	78	0.05	<10	46	<10	21	47

QC DATA:

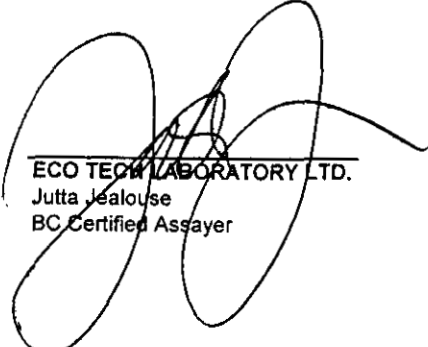
Repeat:

10	L22400N 4725E	<5	0.6	1.76	5	125	<5	0.32	<1	16	54	26	2.90	<10	0.54	1029	2	0.01	29	440	28	<5	<20	13	0.06	<10	61	<10	9	62
19	L22400N 4950E	<5	<0.2	0.83	<5	65	<5	0.21	<1	9	37	10	3.06	<10	0.27	393	2	<0.01	14	420	20	<5	<20	5	0.16	<10	55	<10	<1	38
28	L22800N 4675E		0.5	0.26	<5	215	<5	1.11	<1	<1	3	9	0.53	<10	0.06	14	<1	0.03	5	1130	12	<5	<20	36	<0.01	<10	4	<10	12	6
36	L22800N 4875E	<5	<0.2	1.20	5	35	10	0.12	<1	10	36	13	3.48	<10	0.20	217	3	0.01	15	390	34	<5	<20	<1	0.14	<10	58	<10	2	40
54	L22600N 4825E	<5	<0.2	2.06	10	210	<5	0.34	<1	20	68	30	4.11	<10	0.84	573	4	0.01	46	290	32	<5	<20	13	0.18	<10	81	<10	<1	75
71	L23000N 4750E	<5	<0.2	0.81	5	205	<5	0.35	<1	11	40	14	2.99	<10	0.36	292	<1	0.01	15	170	16	<5	<20	10	0.34	<10	82	<10	<1	41

Standard:

GEO'04		140	1.5	1.22	60	135	<5	1.34	<1	15	54	67	3.58	<10	0.70	563	3	0.02	27	650	30	<5	<20	50	0.05	<10	72	<10	5	74
GEO'04		140	1.4	1.44	65	145	<5	1.43	<1	17	60	79	3.89	<10	0.80	631	1	0.02	29	710	28	<5	<20	55	0.10	<10	83	<10	2	77

JJ/sc
#1/1596/1655
XLS/04


ECO TECH LABORATORY LTD.
Jutta Jealouse
BC Certified Assayer

ECO TECH LABORATORY LTD.
10041 Dallas Drive
KAMLOOPS, B.C.
V2C 6T4

ICP CERTIFICATE OF ANALYSIS AK 2004-1597

NAVASOTA RESOURCES
#207 141 VICTORIA STREET.
KAMLOOPS, BC
V2C 1Z5

Phone: 250-573-5700
Fax : 250-573-4557

No. of samples received: 60
Sample type: Soil
Project #: Not Indicated
Shipment #: Not Indicated

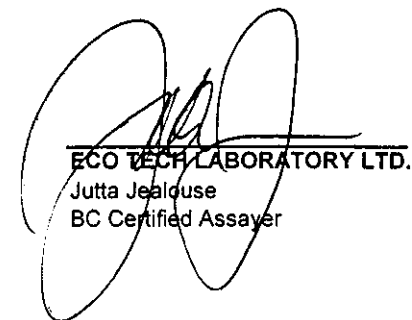
Values in ppm unless otherwise reported

Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
1	L22000N 5025E	30	0.7	1.65	20	115	<5	0.09	<1	14	69	31	3.61	<10	0.82	303	4	<0.01	44	420	50	<5	<20	13	0.05	<10	62	<10	2	95
2	L22000N 5050E	5	0.8	1.38	<5	175	5	0.23	<1	12	44	20	2.87	<10	0.44	420	2	0.01	31	270	28	<5	<20	14	0.12	<10	42	<10	15	155
3	L22000N 5075E	5	0.8	1.14	<5	80	<5	0.14	<1	9	36	14	2.94	<10	0.27	146	1	0.01	20	440	22	<5	<20	6	0.17	<10	41	<10	9	81
4	L22000N 5100E	5	0.9	1.00	<5	130	<5	0.12	<1	11	33	19	2.67	<10	0.28	502	2	0.01	25	710	30	<5	<20	6	0.08	<10	40	<10	2	106
5	L22000N 5125E	5	0.8	0.66	<5	165	<5	0.10	<1	11	22	22	2.82	<10	0.14	680	2	0.01	21	550	26	<5	<20	7	0.03	<10	36	<10	<1	81
6	L22000N 5150E	5	0.8	1.27	<5	305	<5	0.18	<1	14	41	20	2.87	<10	0.39	1128	1	0.01	26	550	22	<5	<20	9	0.08	<10	50	<10	3	95
7	L22000N 5175E	5	0.8	1.03	<5	145	5	0.17	<1	11	37	16	2.75	<10	0.30	617	2	0.01	18	550	14	<5	<20	8	0.10	<10	46	<10	2	69
8	L22000N 5200E	5	0.8	1.35	<5	405	<5	0.35	<1	14	46	33	2.98	<10	0.41	955	1	0.01	28	550	20	<5	<20	19	0.10	<10	51	<10	24	90
9	L22000N 5225E	5	1.0	2.20	<5	400	<5	0.24	2	19	63	41	3.81	<10	0.59	1133	1	0.02	42	460	24	<5	<20	17	0.12	<10	60	<10	10	122
10	L22000N 5250E	5	0.9	1.09	<5	170	5	0.18	<1	10	41	18	3.09	<10	0.29	361	2	0.01	18	370	14	<5	<20	8	0.15	<10	56	<10	6	59
11	L22000N 5275E	5	0.7	0.82	<5	220	5	0.21	<1	12	33	14	2.82	<10	0.24	641	2	0.01	13	350	14	<5	<20	11	0.16	<10	45	<10	9	59
12	L22000N 5300E	10	1.1	1.57	<5	320	<5	0.41	<1	18	51	54	2.94	<10	0.47	963	2	0.01	32	560	18	<5	<20	31	0.10	<10	50	<10	42	73
13	L22000N 5325E	5	0.9	1.43	<5	100	5	0.27	<1	13	56	21	3.02	<10	0.68	284	2	0.01	27	570	14	<5	<20	5	0.14	<10	39	<10	9	51
14	L22000N 5350E	5	0.8	0.37	<5	35	<5	0.07	<1	4	12	6	1.17	<10	0.06	86	<1	0.01	6	340	10	<5	<20	2	0.09	<10	22	<10	6	20
15	L22000N 5375E	25	0.6	2.51	<5	95	10	0.43	<1	18	72	37	3.57	<10	0.99	456	3	0.01	35	660	20	<5	<20	4	0.18	<10	47	<10	18	61
16	L22000N 5400E	10	0.9	1.20	20	180	<5	0.08	<1	20	35	31	3.85	<10	0.34	1143	3	0.01	40	990	36	<5	<20	5	0.03	<10	40	<10	<1	87
17	L22000N 5425E	15	0.9	0.84	5	105	<5	0.05	<1	7	22	17	2.91	<10	0.14	188	3	0.01	25	360	26	<5	<20	5	0.02	<10	42	<10	<1	61
18	L22000N 5450E	15	0.7	0.51	10	105	<5	0.10	<1	7	19	18	2.31	<10	0.13	149	2	0.01	18	270	18	<5	<20	6	0.06	<10	41	<10	<1	49
19	L22000N 5475E	5	2.5	2.30	20	515	<5	0.38	<1	29	50	79	4.76	<10	0.42	5958	3	0.02	68	1270	42	<5	<20	32	0.02	<10	53	<10	33	129
20	L22000N 5500E	10	1.5	1.31	<5	405	<5	0.19	<1	14	30	50	2.99	<10	0.24	1349	2	0.01	39	530	30	<5	<20	19	0.05	<10	37	<10	15	101
21	L22200N 5025E	5	2.0	1.26	5	75	5	0.14	<1	10	40	20	3.07	<10	0.35	248	2	0.01	20	460	24	<5	<20	6	0.12	<10	36	<10	7	58
22	L22200N 5050E	5	1.7	1.14	<5	80	<5	0.09	<1	8	27	17	2.50	<10	0.19	168	3	0.01	14	290	18	<5	<20	5	0.11	<10	28	<10	10	42
23	L22200N 5075E	5	2.2	1.46	<5	250	<5	0.22	1	10	41	38	2.61	<10	0.41	305	2	0.01	36	470	20	<5	<20	21	0.09	<10	40	<10	36	91
24	L22200N 5100E	5	2.0	1.25	<5	240	<5	0.24	2	14	28	56	2.79	<10	0.22	408	2	0.01	36	480	24	<5	<20	28	0.09	<10	39	<10	40	99
25	L22200N 5125E	5	0.8	1.09	<5	235	5	0.37	1	15	44	31	3.25	<10	0.43	637	1	0.01	31	540	26	<5	<20	37	0.10	<10	47	<10	6	107

Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
26	L22200N 5150E	15	1.2	0.69	<5	185	<5	0.24	<1	15	26	37	3.30	<10	0.15	762	2	0.01	30	780	46	<5	<20	16	0.06	<10	48	<10	<1	96
27	L22200N 5175E	15	1.0	0.71	5	145	<5	0.15	<1	10	29	27	2.81	<10	0.20	534	2	0.01	25	910	26	<5	<20	8	0.07	<10	47	<10	<1	71
28	L22200N 5200E	5	0.7	1.08	<5	195	5	0.37	<1	16	38	28	3.13	<10	0.35	753	1	0.01	28	880	26	<5	<20	26	0.07	<10	46	<10	6	72
29	L22200N 5225E	5	1.9	1.46	5	160	<5	0.42	<1	19	33	48	2.77	20	0.36	1509	<1	0.01	54	890	22	<5	<20	48	0.04	<10	47	<10	72	70
30	L22200N 5250E	20	1.1	0.72	20	190	<5	0.30	<1	15	30	31	2.63	<10	0.21	601	1	0.01	27	800	40	<5	<20	28	0.06	<10	47	<10	5	58
31	L22200N 5275E	10	1.1	1.06	5	175	<5	0.22	<1	11	41	31	3.34	<10	0.31	450	2	0.01	26	750	24	<5	<20	15	0.09	<10	58	<10	3	78
32	L22200N 5300E	5	1.5	1.00	<5	125	<5	0.15	<1	15	39	25	2.74	<10	0.32	924	<1	0.01	22	670	18	<5	<20	9	0.08	<10	52	<10	4	67
33	L22200N 5325E	5	1.0	1.74	<5	115	5	0.20	<1	14	54	23	3.23	<10	0.61	525	2	0.01	27	610	18	<5	<20	5	0.11	<10	52	<10	7	73
34	L22200N 5350E	5	2.9	3.25	15	505	<5	0.28	<1	22	82	135	4.71	<10	0.85	546	2	0.02	95	530	42	<5	<20	28	0.10	<10	61	<10	32	123
35	L22200N 5375E	5	2.7	2.38	10	550	<5	0.45	<1	23	65	115	3.76	10	0.74	959	<1	0.02	80	740	32	<5	<20	53	0.07	<10	60	<10	62	102
36	L22200N 5400E	5	1.8	2.09	10	535	<5	0.56	<1	24	55	78	3.34	<10	0.67	1442	2	0.02	62	1520	30	<5	<20	67	0.03	<10	66	<10	46	102
37	L22200N 5425E	10	1.7	1.71	10	470	<5	0.51	<1	18	46	68	2.70	10	0.52	1483	2	0.02	51	1400	30	<5	<20	57	0.02	<10	50	<10	65	87
38	L22200N 5450E	5	1.3	1.07	10	390	<5	0.48	<1	17	37	55	2.69	<10	0.45	1506	2	0.02	41	980	28	<5	<20	53	0.05	<10	44	<10	13	97
39	L22200N 5475E	10	1.4	1.03	10	405	<5	0.52	<1	16	38	55	2.53	<10	0.45	1544	1	0.01	40	990	28	<5	<20	58	0.04	<10	42	<10	13	91
40	L22200N 5500E	5	1.7	1.11	<5	175	<5	0.26	<1	13	33	32	2.74	<10	0.36	891	1	0.01	25	900	22	<5	<20	24	0.05	<10	43	<10	1	76
41	L22400N 5025E	5	1.1	1.15	<5	135	10	0.22	<1	10	38	14	2.68	<10	0.33	438	1	0.01	17	430	18	<5	<20	10	0.15	<10	28	<10	12	49
42	L22400N 5050E	5	1.0	0.85	<5	85	5	0.16	<1	8	26	15	2.10	<10	0.18	205	2	0.01	13	400	14	<5	<20	7	0.11	<10	38	<10	15	36
43	L22400N 5075E	15	0.9	1.59	25	390	<5	0.59	1	21	51	39	3.04	<10	0.51	2057	3	0.01	46	820	50	<5	<20	30	0.09	<10	56	<10	20	181
44	L22400N 5100E	10	1.5	1.38	<5	195	<5	0.33	1	13	46	43	2.80	<10	0.37	532	2	0.01	28	670	24	<5	<20	20	0.12	<10	47	<10	34	64
45	L22400N 5125E	5	0.9	1.26	<5	375	5	0.34	<1	12	45	50	3.32	<10	0.26	493	3	0.01	29	650	24	<5	<20	32	0.12	<10	48	<10	29	98
46	L22400N 5150E	5	0.7	1.49	<5	155	10	0.27	<1	14	54	45	3.65	<10	0.42	549	2	0.01	32	1000	24	<5	<20	16	0.12	<10	54	<10	8	80
47	L22400N 5175E	5	0.8	1.12	<5	240	5	0.25	<1	11	44	31	3.34	<10	0.37	386	3	0.01	28	550	24	<5	<20	19	0.13	<10	57	<10	4	64
48	L22400N 5200E	5	0.5	1.51	<5	175	<5	0.17	<1	16	52	44	3.58	<10	0.52	664	2	0.01	35	850	24	<5	<20	12	0.08	<10	60	<10	<1	91
49	L22400N 5225E	5	0.4	0.89	<5	170	<5	0.24	<1	12	40	22	2.83	<10	0.36	680	2	0.01	21	760	16	<5	<20	13	0.10	<10	52	<10	5	65
50	L22400N 5250E	5	0.4	1.06	<5	145	10	0.12	<1	9	35	19	3.08	<10	0.33	367	2	0.01	19	1040	16	<5	<20	6	0.08	<10	53	<10	1	57
51	L22400N 5275E	5	0.7	1.22	<5	160	5	0.47	<1	13	41	17	2.97	<10	0.41	961	2	0.01	18	1040	18	<5	<20	21	0.10	<10	47	<10	6	74
52	L22400N 5300E	5	0.6	0.56	<5	200	<5	0.23	<1	8	21	18	1.89	<10	0.12	488	1	0.01	11	690	14	<5	<20	16	0.07	<10	36	<10	9	49
53	L22400N 5325E	5	2.0	2.44	10	395	<5	0.34	<1	26	67	81	3.72	<10	0.70	2219	2	0.02	52	990	38	<5	<20	39	0.04	<10	71	<10	32	117
54	L22400N 5350E	<5	2.4	2.29	<5	410	<5	0.31	<1	29	54	101	3.34	10	0.52	1533	3	0.02	54	800	36	<5	<20	36	0.04	<10	64	<10	48	92
55	L22400N 5375E	<5	1.2	0.96	<5	190	<5	0.18	<1	14	28	31	2.15	<10	0.27	669	2	0.01	21	460	18	<5	<20	17	0.06	<10	41	<10	18	52
56	L22400N 5400E	5	2.0	1.99	5	220	<5	0.15	<1	20	54	81	3.62	<10	0.48	564	3	0.01	45	580	32	<5	<20	11	0.07	<10	55	<10	31	86
57	L22400N 5425E	5	1.3	1.32	5	205	<5	0.24	<1	16	40	34	3.23	<10	0.36	1393	2	0.01	30	930	30	<5	<20	12	0.06	<10	44	<10	<1	116
58	L22400N 5450E	5	1.7	1.67	10	170	5	0.16	<1	16	58	45	3.45	<10	0.63	501	2	0.01	44	540	26	<5	<20	10	0.07	<10	53	<10	12	93
59	L22400N 5475E	5	1.8	1.15	<5	180	<5	0.22	<1	14	29	37	2.17	<10	0.26	971	2	0.01	25	980	22	<5	<20	12	0.04	<10	38	<10	13	66
60	L22400N 5500E	5	1.6	1.70	10	155	<5	0.13	<1	17	46	46	2.98	<10	0.45	755	2	0.01	38	630	30	<5	<20	10	0.05	<10	44	<10	10	78

Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn	
QC DATA:																															
<i>Repeat:</i>																															
1	L22000N 5025E	15	0.7	1.61	20	110	<5	0.09	<1	13	67	30	3.52	<10	0.80	303	4	<0.01	44	400	54	<5	<20	13	0.06	<10	60	<10	2	95	
10	L22000N 5250E	5	1.0	1.14	<5	180	5	0.19	<1	10	42	18	3.18	<10	0.30	373	2	0.01	18	390	16	<5	<20	7	0.17	<10	60	<10	6	61	
19	L22000N 5475E	5	2.6	2.39	15	515	<5	0.38	<1	31	52	82	4.96	<10	0.44	5796	1	0.02	73	1270	42	<5	<20	34	0.03	<10	55	<10	33	134	
28	L22200N 5200E	10	0.7	1.05	<5	190	5	0.37	<1	16	38	27	3.17	<10	0.35	772	2	0.01	32	820	26	<5	<20	26	0.08	<10	52	<10	7	82	
36	L22200N 5400E	5	1.8	2.12	5	535	<5	0.55	<1	23	56	78	3.32	<10	0.68	1423	2	0.02	64	1510	34	<5	<20	65	0.03	<10	66	<10	45	102	
45	L22400N 5125E	5	1.0	1.28	<5	375	5	0.35	<1	12	45	50	3.33	<10	0.26	497	2	0.01	30	660	22	<5	<20	32	0.11	<10	47	<10	28	98	
54	L22400N 5350E	5	2.5	2.53	5	445	<5	0.33	<1	32	59	109	3.62	10	0.57	1618	3	0.02	58	850	38	<5	<20	38	0.05	<10	69	<10	51	100	
<i>Standard:</i>																															
GEO'04		140	1.6	1.45	50	140	<5	1.26	<1	18	56	86	2.97	<10	0.78	550	<1	0.03	25	610	24	<5	<20	51	0.11	<10	64	<10	9	76	
GEO'04		140	1.6	1.49	50	140	<5	1.30	<1	16	58	84	3.02	<10	0.79	563	<1	0.03	27	640	22	<5	<20	53	0.11	<10	62	<10	10	74	

JJ/jm
jf/1597
XLS/04


ECO TECH LABORATORY LTD.
 Jutta Jealous
 BC Certified Assayer

ECO TECH LABORATORY LTD.
10041 Dallas Drive
KAMLOOPS, B.C.
V2C 6T4

ICP CERTIFICATE OF ANALYSIS AK 2004-1598

NAVASOTA RESOURCES
#207 141 VICTORIA STREET
KAMLOOPS, BC
V2C 1Z5

Phone: 250-573-5700
Fax : 250-573-4557

No. of samples received: 80
Sample type: Soil
Project #: Not Indicated
Shipment #: Not Indicated

Values in ppm unless otherwise reported

Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
1	L23100N 4500E	5	0.6	1.47	<5	155	<5	0.18	<1	10	35	31	2.35	<10	0.34	310	2	0.01	17	410	22	<5	<20	8	0.10	<10	50	<10	14	35
2	L23100N 4525E	5	0.3	2.63	10	165	5	0.41	<1	23	71	31	3.99	<10	0.75	689	2	0.01	39	390	26	<5	<20	9	0.12	<10	80	<10	13	66
3	L23100N 4550E	10	0.2	2.00	<5	105	<5	0.24	<1	15	53	25	3.57	<10	0.59	352	1	0.01	26	340	22	<5	<20	2	0.16	<10	49	<10	3	52
4	L23100N 4575E	<5	0.2	2.14	<5	110	<5	0.26	<1	17	58	28	3.61	<10	0.72	380	3	0.01	32	340	24	<5	<20	4	0.16	<10	50	<10	5	53
5	L23100N 4600E	5	0.2	2.39	<5	175	<5	0.47	<1	23	77	34	3.89	<10	1.01	559	2	0.01	45	290	26	<5	<20	6	0.19	<10	56	<10	8	63
6	L23100N 4625E	5	0.2	1.21	<5	85	<5	0.40	<1	10	34	15	3.02	<10	0.32	270	2	0.01	14	370	18	<5	<20	9	0.17	<10	46	<10	<1	37
7	L23100N 4650E	<5	0.2	1.78	<5	70	5	0.22	<1	16	56	23	4.03	<10	0.52	602	2	0.01	25	410	20	<5	<20	2	0.23	<10	55	<10	<1	47
8	L23100N 4675E	<5	0.2	2.22	<5	65	<5	0.16	<1	14	51	17	5.38	<10	0.47	300	3	0.01	19	470	22	<5	<20	<1	0.25	<10	68	<10	<1	56
9	L23100N 4700E	<5	<0.2	1.06	<5	145	5	0.19	<1	11	37	12	3.19	<10	0.37	351	2	0.01	15	330	16	<5	<20	2	0.16	<10	56	<10	<1	49
10	L23100N 4725E	5	<0.2	1.24	<5	75	5	0.14	<1	10	39	17	3.72	<10	0.38	215	3	0.01	16	260	20	<5	<20	1	0.15	<10	46	<10	<1	35
11	L23100N 4750E	5	0.8	2.67	20	130	<5	0.17	<1	10	39	62	3.52	20	0.19	227	3	0.01	18	700	28	<5	<20	6	0.07	<10	62	<10	32	46
12	L23100N 4775E	5	0.2	1.08	<5	105	<5	0.15	<1	10	37	17	3.74	<10	0.39	175	1	0.01	16	280	16	<5	<20	<1	0.19	<10	64	<10	<1	41
13	L23100N 4800E	5	0.2	0.99	<5	75	<5	0.09	<1	7	27	11	3.08	<10	0.21	103	2	0.01	10	180	18	<5	<20	1	0.18	<10	46	<10	<1	30
14	L23100N 4825E	5	0.2	0.87	<5	50	<5	0.05	<1	6	17	9	2.61	<10	0.09	206	2	0.01	6	330	14	<5	<20	1	0.12	<10	41	<10	<1	22
15	L23100N 4850E	5	0.2	1.13	<5	105	5	0.22	<1	14	33	12	3.04	<10	0.32	836	3	0.01	15	280	20	<5	<20	3	0.14	<10	47	<10	<1	40
16	L23100N 4875E	10	0.4	1.46	<5	145	<5	0.36	<1	13	32	36	2.42	<10	0.32	922	3	0.02	20	330	22	<5	<20	7	0.11	<10	39	<10	8	43
17	L23100N 4900E	5	0.2	0.41	<5	70	<5	0.04	<1	4	10	15	2.28	<10	0.04	164	3	0.01	4	450	18	<5	<20	<1	0.06	<10	35	<10	<1	25
18	L23100N 4925E	5	0.6	2.43	5	285	<5	0.65	<1	15	11	21	1.69	<10	0.06	324	2	0.01	11	740	32	<5	<20	41	0.01	<10	19	<10	17	48
19	L23100N 4950E	5	0.2	1.66	15	185	5	0.39	<1	15	34	22	6.03	<10	0.44	304	5	0.01	22	410	18	<5	<20	16	0.09	<10	95	<10	<1	90
20	L23100N 4975E	5	0.2	1.12	<5	265	<5	0.76	<1	4	7	17	1.56	<10	0.10	404	2	0.02	7	570	12	<5	<20	47	0.04	<10	27	<10	3	20
21	L23100N 5025E	<5	0.4	0.70	<5	75	5	0.19	<1	8	24	13	2.67	<10	0.23	127	1	0.01	8	290	18	<5	<20	4	0.21	<10	39	<10	<1	29
22	L23100N 5050E	30	0.4	1.05	<5	90	10	0.19	<1	11	36	18	3.43	<10	0.38	214	2	0.01	15	300	16	<5	<20	4	0.17	<10	50	<10	<1	40
23	L23100N 5075E	5	0.9	1.97	<5	80	<5	0.21	<1	13	51	47	4.44	<10	0.53	258	4	0.01	26	520	20	<5	<20	6	0.13	<10	36	<10	1	80
24	L23100N 5100E	15	1.2	0.76	35	50	<5	0.04	<1	7	10	50	3.99	<10	0.05	167	8	0.01	29	830	24	<5	<20	<1	0.07	<10	33	<10	<1	103
25	L23100N 5125E	5	0.9	0.52	25	110	<5	0.05	<1	12	7	21	3.84	<10	0.03	1336	5	0.01	17	830	44	<5	<20	4	0.03	<10	34	<10	<1	104

N.	OTA	JURC	ICP																		SIS										J04-1										EC										CH L										IATC										TD									
Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn																																																		
26	L23100N 5150E	5	0.9	0.50	20	105	<5	0.04	<1	12	7	21	3.81	<10	0.03	1194	5	0.01	19	830	44	<5	<20	3	0.03	<10	35	<10	<1	103																																																		
27	L23100N 5175E	10	2.6	0.57	30	360	<5	0.69	2	10	15	25	3.39	<10	0.12	1377	7	0.01	34	650	84	<5	<20	41	0.03	<10	44	<10	<1	234																																																		
28	L23100N 5200E	5	1.0	1.27	30	125	<5	0.20	1	24	26	31	4.09	<10	0.25	2745	4	<0.01	37	780	50	<5	<20	10	0.03	<10	56	<10	11	157																																																		
29	L23100N 5225E	5	0.4	0.57	10	120	<5	0.14	<1	9	21	19	2.96	<10	0.11	580	4	<0.01	16	400	26	<5	<20	6	0.08	<10	65	<10	<1	79																																																		
30	L23100N 5250E	5	0.4	1.21	10	170	<5	0.09	<1	20	37	32	3.75	<10	0.33	1178	3	0.01	31	620	36	<5	<20	5	0.05	<10	72	<10	<1	140																																																		
31	L23100N 5275E	5	0.8	0.61	15	115	<5	0.16	<1	11	23	15	2.87	<10	0.20	1225	4	<0.01	18	650	26	<5	<20	3	0.07	<10	58	<10	<1	91																																																		
32	L23100N 5300E	25	0.3	1.57	15	100	<5	0.25	<1	17	50	35	3.73	<10	0.70	500	4	0.01	38	750	34	<5	<20	8	0.08	<10	57	<10	3	116																																																		
33	L23100N 5325E	10	0.7	2.48	15	195	<5	0.35	<1	28	78	69	4.67	<10	1.10	770	3	0.01	82	550	38	<5	<20	19	0.08	<10	70	<10	9	212																																																		
34	L23100N 5350E	5	0.6	1.44	5	160	<5	0.13	<1	11	45	38	4.24	<10	0.36	355	4	0.01	26	450	28	<5	<20	6	0.10	<10	68	<10	<1	84																																																		
35	L23100N 5375E	10	0.6	1.30	5	140	<5	0.11	<1	11	40	34	3.81	<10	0.33	336	4	0.01	25	370	26	<5	<20	4	0.10	<10	65	<10	<1	77																																																		
36	L23100N 5400E	5	1.1	0.78	<5	140	<5	0.20	<1	9	29	15	2.78	<10	0.28	1008	<1	<0.01	20	750	20	<5	<20	8	0.03	<10	54	<10	<1	66																																																		
37	L23100N 5425E	10	0.5	1.08	<5	100	<5	0.08	<1	9	31	15	3.12	<10	0.26	539	2	0.01	15	630	18	<5	<20	2	0.05	<10	57	<10	<1	56																																																		
38	L23100N 5450E	5	0.9	1.09	5	165	5	0.32	<1	19	39	50	3.61	<10	0.35	1094	2	0.01	36	680	30	<5	<20	32	0.04	<10	57	<10	3	70																																																		
39	L23100N 5475E	5	1.4	1.15	5	95	<5	0.17	<1	13	38	64	3.79	<10	0.25	610	2	0.01	32	680	26	<5	<20	15	0.04	<10	58	<10	3	64																																																		
40	L23100N 5500E	10	4.2	2.16	15	220	<5	0.37	1	28	57	141	4.59	<10	0.38	2477	2	0.02	89	1120	40	<5	<20	43	0.03	<10	51	<10	35	119																																																		
41	L23200N 4500E	5	1.0	5.01	20	570	<5	0.26	<1	20	116	124	5.35	<10	1.00	511	2	0.02	73	580	54	<5	<20	17	0.11	<10	107	<10	36	110																																																		
42	L23200N 4525E	5	1.4	5.19	20	605	10	0.30	<1	28	136	151	7.50	<10	1.16	547	3	0.02	82	440	56	<5	<20	22	0.16	<10	141	<10	24	134																																																		
43	L23200N 4550E	10	0.2	2.86	5	170	<5	0.14	<1	4	42	45	1.39	20	0.21	67	<1	0.02	20	600	28	<5	<20	5	0.04	<10	37	<10	40	22																																																		
44	L23200N 4575E	5	0.2	2.61	<5	110	10	0.36	<1	22	85	29	4.30	<10	0.94	367	1	0.01	43	280	28	<5	<20	6	0.21	<10	31	<10	13	53																																																		
45	L23200N 4600E	5	0.3	2.83	<5	100	10	0.31	<1	32	89	30	4.85	<10	0.98	907	1	0.01	45	370	28	<5	<20	4	0.22	<10	33	<10	9	76																																																		
46	L23200N 4625E	5	0.6	2.85	<5	105	10	0.31	<1	33	90	30	4.88	<10	1.00	903	<1	0.01	46	370	26	<5	<20	3	0.25	<10	40	<10	10	75																																																		
47	L23200N 4650E	5	0.6	1.89	15	340	<5	0.68	<1	36	51	28	4.30	<10	0.47	3780	3	0.02	27	1340	28	<5	<20	27	0.03	<10	149	<10	12	79																																																		
48	L23200N 4675E	5	0.7	2.09	25	275	5	0.44	<1	23	56	31	3.67	<10	0.53	1286	3	0.01	30	1320	28	<5	<20	15	0.03	<10	130	<10	19	68																																																		
49	L23200N 4700E	5	0.3	3.11	20	115	<5	0.68	<1	14	27	50	2.60	10	0.18	1332	3	0.02	16	1240	28	<5	<20	20	0.02	<10	64	<10	34	47																																																		
50	L23200N 4725E	5	0.2	1.58	<5	55	<5	0.10	<1	5	8	16	1.40	<10	0.07	97	<1	0.01	5	450	18	<5	<20	3	0.05	<10	18	<10	8	23																																																		
51	L23200N 4750E	5	0.8	2.16	15	165	<5	1.07	<1	15	32	72	2.06	<10	0.16	2963	1	0.02	29	1930	20	<5	<20	22	0.01	<10	83	<10	36	84																																																		
52	L23200N 4775E	<5	1.0	3.04	15	155	<5	0.53	<1	14	40	72	2.15	20	0.21	2823	1	0.02	21	1540	30	<5	<20	14	0.02	<10	62	<10	58	47																																																		
53	L23200N 4800E	5	0.4	2.49	10	160	<5	0.56	<1	14	39	33	2.27	10	0.37	1580	2	0.01	22	1040	24	<5	<20	14	0.04	<10	58	<10	28	43																																																		
54	L23200N 4825E	5	0.2	0.89	<5	85	10	0.20	<1	8	27	11	2.70	<10	0.24	127	1	0.01	11	230	16	<5	<20	2	0.14	<10	27	<10	2	29																																																		
55	L23200N 4850E	5	0.2	1.93	<5	90	10	0.14	<1	12	44	17	4.56	<10	0.42	231	3	<0.01	19	340	24	<5	<20	2	0.14	<10	34	<10	2	45																																																		
56	L23200N 4875E	5	<0.2	2.42	<5	95	5	0.20	<1	16	61	30	4.50	<10	0.75	278	2	<0.01	30	340	26	<5	<20	<1	0.18	<10	38	<10	3	56																																																		
57	L23200N 4900E	5	<0.2	1.23	<5	85	10	0.17	<1	12	44	15	3.67	<10	0.40	173	2	0.01	17	270	20	<5	<20	<1	0.18	<10	57	<10	3	34																																																		
58	L23200N 4925E	5	0.4	3.03	10	420	<5	1.26	<1	15	29	67	2.61	<10	0.32	2763	1	0.02	30	1480	26	<5	<20	84	0.03	<10	41	<10	30	47																																																		
59	L23200N 4950E	5	0.8	3.36	10	425	<5	0.78	<1	27	45	124	4.74	<10	0.50	1329	2	0.02	63	830	36	<5	<20	54	0.08	<10	47	<10	21	89																																																		
60	L23200N 4975E	5	0.2	1.61	<5	210	<5	0.59	<1	15	30	31	2.54	<10	0.30	3833	1	0.01	17	830	24	<5	<20	30	0.07	<10	59	<10	18	49																																																		
61	L23200N 5025E	5	0.7	1.99	5	100	<5	0.30	<1	5	28	26	1.67	<10	0.24	122	1	0.02	25	1000	22	<5	<20	28	0.02	<10	48	<10	22	56																																																		
62	L23200N 5050E	20	0.8	0.44	5	60	<5	0.10	<1	5	10	14	1.94	<10	0.06	69	2	0.01	10	230	72	<5	<20	10	0.07	<10	21	<10	<1	56																																																		
63	L23200N 5075E	10	0.4	0.23	10	35	<5	0.04	<1	3	5	12	1.67	<10	0.02	58	3	0.01	8	380	16	<5	<20	1	0.03	<10	31	<10	<1	56																																																		
64	L23200N 5100E	35	1.3	1.50	405	225	20	0.03	<1	97	18	177	>10	<10	<0.01	6318	38	<0.01	37	>10000	62	<5	<20	57	0.02	<10	65	<10	<1	167																																																		
65	L23200N 5125E	5	1.1	0.80	10	65	<5	0.06	<1	6	14	27	3.47	<10	0.09	240	4	0.01	12	1190	32	<5	<20	2	0.03	<10	36	<10	<1	70																																																		

N	OTA	JUR	ICP TIFIC OF A SIS 004-																	EC	CH L	ATC	TD							
Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
66	L23200N 5150E	20	1.6	0.69	20	220	<5	0.09	1	14	11	33	3.67	<10	0.09	2210	5	<0.01	34	750	48	<5	<20	7	0.02	<10	29	<10	<1	189
67	L23200N 5175E	5	0.5	1.18	10	140	10	0.24	<1	13	35	19	3.90	<10	0.34	522	3	0.01	24	630	34	<5	<20	12	0.10	<10	55	<10	<1	144
68	L23200N 5200E	5	0.5	1.05	5	100	5	0.16	<1	10	34	23	3.58	<10	0.29	244	3	<0.01	19	500	24	<5	<20	7	0.08	<10	56	<10	<1	70
69	L23200N 5225E	5	0.8	1.58	5	105	<5	0.49	2	13	27	47	2.91	<10	0.16	913	2	0.01	31	910	24	<5	<20	51	0.03	<10	53	<10	13	85
70	L23200N 5250E	5	0.2	0.43	<5	85	<5	0.09	<1	6	20	16	1.98	<10	0.09	122	2	<0.01	12	370	20	<5	<20	3	0.05	<10	49	<10	<1	50
71	L23200N 5275E	20	0.4	1.77	20	115	<5	0.23	<1	20	53	40	4.04	<10	0.71	707	5	0.01	47	520	38	<5	<20	10	0.10	<10	60	<10	4	135
72	L23200N 5300E	10	0.7	1.39	10	125	5	0.12	<1	16	46	32	4.06	<10	0.43	918	3	0.01	27	470	28	<5	<20	4	0.09	<10	71	<10	<1	95
73	L23200N 5325E	15	0.4	1.90	20	120	<5	0.16	<1	17	66	33	4.57	<10	0.93	502	4	<0.01	53	830	28	<5	<20	4	0.07	<10	70	<10	<1	97
74	L23200N 5350E	10	1.7	2.17	20	220	<5	0.39	<1	24	65	87	4.42	<10	0.64	1851	4	0.01	52	730	36	<5	<20	40	0.04	<10	69	<10	37	111
75	L23200N 5375E	5	1.2	2.47	15	340	<5	0.55	1	30	76	117	4.47	<10	0.73	1890	3	0.02	73	870	42	<5	<20	53	0.05	<10	73	<10	31	170
76	L23200N 5400E	5	1.3	1.19	5	145	<5	0.26	<1	10	38	74	3.39	<10	0.24	246	3	0.01	31	580	24	<5	<20	26	0.08	<10	61	<10	10	56
77	L23200N 5425E	5	0.9	1.76	10	160	<5	0.34	<1	20	51	77	3.92	<10	0.50	862	3	0.01	43	700	30	<5	<20	35	0.07	<10	56	<10	10	98
78	L23200N 5450E	5	1.4	1.79	10	200	<5	0.55	1	19	45	99	3.29	<10	0.42	2484	3	0.01	49	1260	28	<5	<20	60	0.03	<10	59	<10	34	97
79	L23200N 5475E	5	1.8	2.01	15	235	<5	0.55	<1	21	58	100	3.65	<10	0.57	1759	3	0.01	64	1440	34	<5	<20	62	0.02	<10	59	<10	43	121
80	L23200N 5500E	5	1.7	2.22	15	250	<5	0.60	1	23	64	129	3.59	<10	0.47	2004	3	0.01	71	1650	36	<5	<20	68	0.02	<10	56	<10	58	111

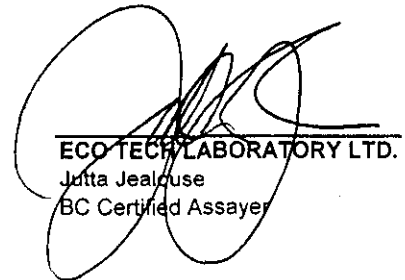
QC DATA:

Repeat:

1	L23100N 4500E	5	0.5	1.48	<5	155	<5	0.19	<1	10	36	30	2.38	<10	0.35	299	2	0.01	17	410	22	<5	<20	6	0.10	<10	50	<10	13	36
10	L23100N 4725E	5	0.2	1.30	<5	80	<5	0.16	<1	10	40	17	3.80	<10	0.39	218	3	0.01	16	280	18	<5	<20	1	0.15	<10	46	<10	<1	36
19	L23100N 4950E	5	0.3	1.66	20	190	5	0.39	<1	15	33	22	5.99	<10	0.43	312	6	0.01	23	410	20	<5	<20	17	0.09	<10	92	<10	<1	92
28	L23100N 5200E	5	1.2	1.22	25	125	<5	0.19	1	23	25	30	3.91	<10	0.24	2740	4	0.01	35	730	48	<5	<20	10	0.03	<10	54	<10	9	154
36	L23100N 5400E	15	1.1	0.88	5	155	<5	0.23	<1	10	33	16	2.86	<10	0.31	1181	1	0.01	19	780	22	<5	<20	8	0.03	<10	57	<10	<1	70
37	L23100N 5425E	15																												
45	L23200N 4600E	15	0.3	2.90	<5	100	15	0.33	<1	32	90	30	4.93	<10	1.00	892	1	0.01	47	420	30	<5	<20	2	0.27	<10	44	<10	11	77
54	L23200N 4825E	5	0.3	0.91	<5	85	5	0.21	<1	8	26	11	2.69	<10	0.23	124	1	0.01	10	240	18	<5	<20	2	0.13	<10	24	<10	3	30
56	L23200N 4875E	5																												
63	L23200N 5075E	5	0.4	0.23	10	35	<5	0.04	<1	3	6	12	1.71	<10	0.02	60	3	0.01	9	380	16	<5	<20	<1	0.03	<10	33	<10	<1	55
71	L23200N 5275E	20	0.3	1.80	25	125	<5	0.24	<1	20	52	42	4.04	<10	0.68	756	3	0.01	44	560	38	<5	<20	11	0.09	<10	57	<10	3	137

Standard:

GEO'04	145	1.6	1.42	50	130	<5	1.26	<1	16	52	88	3.52	<10	0.76	571	<1	0.02	24	590	22	<5	<20	51	0.07	<10	67	<10	9	74
GEO'04	140	1.4	1.55	50	135	<5	1.40	<1	17	59	86	3.81	<10	0.82	575	<1	0.03	26	650	22	<5	<20	60	0.06	<10	66	<10	10	75
GEO'04	135	1.4	1.58	50	140	<5	1.35	<1	17	58	88	3.82	<10	0.82	632	<1	0.02	27	660	24	<5	<20	59	0.08	<10	62	<10	9	75


ECO TECH LABORATORY LTD.
 Jutta Jealouse
 BC Certified Assayer

ECO TECH LABORATORY LTD.
10041 Dallas Drive
KAMLOOPS, B.C.
V2C 6T4

ICP CERTIFICATE OF ANALYSIS AK 2004-1600

NAVASOTA RESOURCES
#207 141 VICTORIA STREET
KAMLOOPS, BC
V2C 1Z5

Phone: 250-573-5700
Fax : 250-573-4557

No. of samples received: 100
Sample type: Soil
Project #: Not Indicated
Shipment #: Not Indicated

Values in ppm unless otherwise reported

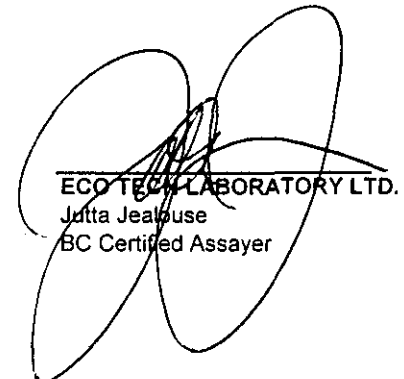
Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
1	L22600N 5025E	5	0.8	0.66	<5	60	<5	0.13	<1	7	24	10	2.47	<10	0.15	365	1	0.01	8	380	16	<5	<20	2	0.12	<10	56	<10	<1	28
2	L22600N 5050E	5	1.2	1.30	<5	110	<5	0.16	<1	10	36	29	2.50	<10	0.31	344	1	0.01	19	520	22	<5	<20	5	0.11	<10	68	<10	3	38
3	L22600N 5075E	5	0.9	0.80	<5	100	<5	0.25	<1	9	31	13	2.76	<10	0.24	568	<1	0.01	13	460	14	<5	<20	6	0.15	<10	66	<10	<1	44
4	L22600N 5100E	5	0.9	0.87	<5	100	<5	0.23	<1	9	32	14	2.95	<10	0.25	497	1	0.01	14	480	14	<5	<20	5	0.17	<10	70	<10	<1	45
5	L22600N 5125E	5	1.2	1.67	5	225	<5	0.60	4	17	44	60	4.08	<10	0.45	727	2	0.01	45	640	28	<5	<20	70	0.10	<10	66	<10	11	127
6	L22600N 5150E	20	0.9	0.62	<5	120	<5	0.33	<1	17	27	39	3.73	<10	0.14	539	3	0.01	28	970	22	<5	<20	35	0.06	<10	62	<10	<1	65
7	L22600N 5175E	10	0.8	1.07	<5	65	<5	0.16	<1	10	41	34	3.90	<10	0.25	241	2	0.01	21	790	18	<5	<20	7	0.15	<10	77	<10	<1	50
8	L22600N 5200E	10	0.8	0.99	10	200	<5	0.41	<1	28	36	39	4.71	<10	0.35	1647	3	0.01	45	1270	30	<5	<20	45	0.05	<10	68	<10	<1	116
9	L22600N 5225E	5	1.1	0.99	15	170	<5	0.30	<1	17	38	31	3.90	<10	0.32	1504	2	0.01	29	1470	32	<5	<20	20	0.07	<10	81	<10	<1	89
10	L22600N 5250E	<5	2.4	0.74	<5	210	<5	0.38	<1	12	32	17	2.81	<10	0.27	1638	1	0.01	16	840	18	<5	<20	10	0.10	<10	67	<10	<1	78
11	L22600N 5275E	20	0.8	2.20	<5	90	<5	0.46	<1	18	67	25	4.09	<10	0.92	432	1	0.01	32	830	18	<5	<20	5	0.18	<10	60	<10	2	87
12	L22600N 5300E	5	0.8	1.11	<5	130	<5	0.26	<1	14	47	19	3.63	<10	0.44	758	2	0.01	19	770	16	<5	<20	2	0.17	<10	76	<10	<1	69
13	L22600N 5325E	15	0.7	0.95	<5	85	<5	0.16	<1	15	33	18	3.81	<10	0.23	1561	2	0.02	12	1360	18	<5	<20	3	0.12	<10	79	<10	<1	63
14	L22600N 5350E	<5	0.7	0.69	<5	75	<5	0.16	<1	8	27	13	2.91	<10	0.26	175	2	0.01	14	450	16	<5	<20	5	0.18	<10	55	<10	<1	41
15	L22600N 5375E	5	1.0	1.02	<5	100	<5	0.13	<1	5	19	20	1.89	<10	0.17	90	1	0.01	10	370	16	<5	<20	6	0.08	<10	31	<10	2	27
16	L22600N 5400E	10	1.5	0.98	15	145	<5	0.26	<1	13	37	19	3.34	<10	0.36	1344	2	0.01	26	650	22	<5	<20	7	0.06	<10	56	<10	<1	72
17	L22600N 5425E	5	1.1	1.92	10	120	<5	0.18	<1	17	49	34	3.78	<10	0.53	517	2	0.01	28	530	28	<5	<20	5	0.12	<10	61	<10	4	82
18	L22600N 5450E	5	1.1	1.56	5	185	<5	0.23	<1	19	52	51	4.23	<10	0.58	499	2	0.01	37	620	26	<5	<20	9	0.09	<10	58	<10	2	74
19	L22600N 5475E	5	0.9	2.02	10	200	<5	0.21	<1	24	69	44	4.40	<10	0.89	662	2	0.01	52	460	26	<5	<20	6	0.09	<10	76	<10	7	96
20	L22600N 5500E	5	1.5	1.15	5	210	<5	0.31	<1	12	38	43	3.08	<10	0.36	831	3	0.01	32	810	22	<5	<20	20	0.06	<10	66	<10	5	63
21	L23300N 4500E	5	1.1	4.68	25	415	<5	0.34	<1	23	96	86	5.08	<10	0.77	551	2	0.02	65	610	44	<5	<20	13	0.13	<10	105	<10	42	107
22	L23300N 4525E	5	0.5	2.58	<5	140	<5	0.35	<1	23	78	40	4.10	<10	1.01	509	2	0.01	46	290	24	<5	<20	5	0.20	<10	62	<10	7	65
23	L23300N 4550E	5	0.5	1.12	<5	95	<5	0.19	<1	8	32	15	3.02	<10	0.25	224	2	0.01	13	340	16	<5	<20	5	0.16	<10	57	<10	<1	33
24	L23300N 4575E	10	0.5	1.20	<5	70	<5	0.17	<1	12	43	16	3.74	<10	0.42	322	2	0.01	18	320	16	<5	<20	2	0.20	<10	65	<10	<1	40
25	L23300N 4600E	20	0.5	2.82	<5	155	<5	0.31	<1	22	79	41	4.45	<10	1.02	509	2	0.01	44	370	24	<5	<20	3	0.17	<10	68	<10	6	72

Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
26	L23300N 4625E	5	0.5	0.78	<5	330	<5	0.26	<1	13	43	28	2.28	<10	0.19	1039	1	0.01	17	480	16	<5	<20	6	0.08	<10	74	<10	<1	56
27	L23300N 4650E	5	1.1	2.96	10	315	<5	0.45	<1	20	69	56	3.88	<10	0.76	1020	2	0.02	43	550	28	<5	<20	11	0.11	<10	85	<10	17	78
28	L23300N 4675E	5	1.0	2.53	10	325	<5	0.53	<1	18	67	45	4.01	<10	0.71	610	4	0.02	43	670	24	<5	<20	18	0.07	<10	94	<10	8	95
29	L23300N 4700E	5	0.4	0.99	<5	70	<5	0.13	<1	8	31	15	3.00	<10	0.19	131	2	0.01	12	200	14	<5	<20	2	0.18	<10	59	<10	<1	33
30	L23300N 4725E	5	0.4	0.64	<5	75	<5	0.13	<1	4	13	10	1.66	<10	0.07	78	1	0.01	5	270	14	<5	<20	2	0.07	<10	27	<10	<1	20
31	L23300N 4750E	5	0.6	1.49	<5	30	<5	0.04	<1	4	19	24	2.10	<10	0.06	111	2	0.01	3	530	18	<5	<20	<1	0.07	<10	37	<10	<1	18
32	L23300N 4775E	5	0.5	0.42	<5	35	<5	0.03	<1	3	11	9	1.39	<10	0.04	52	1	0.01	3	360	14	<5	<20	<1	0.06	<10	24	<10	<1	14
33	L23300N 4800E	5	0.6	1.20	<5	130	<5	0.11	<1	9	38	16	3.09	<10	0.49	274	2	0.01	18	320	16	<5	<20	4	0.08	<10	72	<10	<1	43
34	L23300N 4825E	5	0.6	0.74	<5	65	<5	0.19	<1	8	27	11	2.32	<10	0.23	252	<1	0.01	10	360	14	<5	<20	3	0.13	<10	54	<10	<1	30
35	L23300N 4850E	5	0.6	1.99	<5	100	<5	0.24	<1	14	59	23	3.87	<10	0.70	274	2	0.01	28	320	20	<5	<20	2	0.17	<10	58	<10	<1	53
36	L23300N 4875E	10	0.8	1.58	<5	150	5	0.16	<1	15	48	16	3.27	<10	0.63	609	1	0.01	22	260	18	<5	<20	4	0.13	<10	72	<10	1	51
37	L23300N 4900E	10	0.7	1.19	10	95	<5	0.06	<1	10	39	18	3.85	<10	0.44	212	3	<0.01	25	260	20	<5	<20	<1	0.06	<10	74	<10	<1	57
38	L23300N 4925E	5	0.7	1.21	<5	90	<5	0.05	<1	8	37	15	3.60	<10	0.33	171	3	<0.01	17	290	22	<5	<20	<1	0.06	<10	74	<10	<1	43
39	L23300N 4950E	<5	1.0	1.16	5	115	<5	0.12	<1	8	16	15	1.87	<10	0.16	594	2	0.01	9	340	20	<5	<20	8	0.06	<10	39	<10	3	34
40	L23300N 4975E	5	0.5	1.59	<5	80	<5	0.18	<1	12	49	21	3.86	<10	0.55	245	2	0.01	22	230	18	<5	<20	2	0.19	<10	66	<10	<1	42
41	L23300N 5025E	5	0.9	1.93	15	205	<5	1.16	1	13	36	32	2.02	<10	0.54	904	1	0.01	30	930	20	<5	<20	67	0.05	<10	43	<10	19	91
42	L23300N 5050E	5	0.7	0.43	<5	40	<5	0.07	<1	4	13	8	1.51	<10	0.05	78	1	0.01	6	300	12	<5	<20	<1	0.09	<10	45	<10	<1	17
43	L23300N 5075E	10	1.4	0.98	35	45	<5	0.05	<1	3	7	13	2.50	<10	0.02	100	8	0.01	12	620	32	<5	<20	3	0.05	<10	27	<10	<1	58
44	L23300N 5100E	15	1.4	0.22	10	35	<5	0.03	<1	5	5	10	2.63	<10	0.01	83	5	<0.01	17	330	12	<5	<20	1	0.02	<10	55	<10	<1	56
45	L23300N 5125E	15	1.0	0.41	10	60	<5	0.12	<1	6	15	15	2.79	<10	0.05	198	4	0.01	13	630	24	<5	<20	3	0.08	<10	71	<10	<1	63
46	L23300N 5150E	10	1.3	0.98	30	160	<5	0.22	<1	25	23	37	3.81	<10	0.18	2635	4	0.01	35	750	32	<5	<20	13	0.03	<10	65	<10	<1	141
47	L23300N 5175E	10	0.6	1.27	<5	230	5	0.23	<1	18	40	22	3.26	<10	0.41	790	3	0.01	19	400	22	<5	<20	5	0.14	<10	52	<10	2	47
48	L23300N 5200E	65	0.9	1.81	30	125	<5	0.32	<1	23	50	47	4.52	<10	0.67	1065	2	0.01	61	630	42	<5	<20	16	0.09	<10	56	<10	18	142
49	L23300N 5225E	30	0.9	0.54	<5	140	<5	0.25	<1	7	19	15	2.05	<10	0.11	735	2	0.01	9	420	18	<5	<20	11	0.10	<10	50	<10	<1	60
50	L23300N 5250E	10	1.8	1.64	10	125	<5	0.44	2	15	43	50	3.32	<10	0.49	1322	1	0.01	29	610	24	<5	<20	36	0.11	<10	64	<10	28	81
51	L23300N 5275E	20	0.9	1.42	10	105	<5	0.30	<1	13	41	27	3.31	<10	0.47	570	2	0.01	23	500	24	<5	<20	16	0.12	<10	57	<10	3	75
52	L23300N 5300E	5	0.3	2.77	15	270	<5	0.53	1	26	64	74	4.01	<10	0.65	2713	2	0.02	74	760	38	<5	<20	49	0.07	<10	63	<10	37	124
53	L23300N 5325E	10	1.2	1.81	10	180	<5	0.36	<1	20	51	40	3.51	<10	0.58	1628	1	0.01	39	670	28	<5	<20	28	0.06	<10	58	<10	9	106
54	L23300N 5350E	5	2.2	2.14	10	130	<5	0.11	<1	18	40	24	3.95	<10	0.35	1157	2	0.01	21	1020	28	<5	<20	3	0.05	<10	57	<10	<1	90
55	L23300N 5375E	10	1.6	2.84	10	90	<5	0.08	<1	12	47	22	4.10	<10	0.34	562	3	0.01	25	850	30	<5	<20	1	0.05	<10	41	<10	<1	74
56	L23300N 5400E	5	1.2	1.91	10	75	<5	0.09	<1	12	37	18	3.36	<10	0.32	629	3	0.01	19	590	26	<5	<20	<1	0.06	<10	56	<10	<1	60
57	L23300N 5425E	5	1.5	1.48	15	100	<5	0.11	<1	14	42	23	4.40	<10	0.45	553	4	0.01	34	790	24	<5	<20	4	0.05	<10	64	<10	<1	105
58	L23300N 5450E	10	1.1	1.93	15	115	<5	0.11	<1	17	51	46	3.93	<10	0.61	376	2	0.01	56	400	32	<5	<20	6	0.04	<10	51	<10	4	107
59	L23300N 5475E	15	6.7	4.67	25	290	<5	0.32	<1	20	69	162	4.50	<10	0.55	564	3	0.03	150	910	58	<5	<20	35	0.09	<10	20	<10	42	128
60	L23300N 5500E	5	1.6	2.26	20	265	<5	0.37	<1	24	57	87	4.84	<10	0.55	760	4	0.02	80	920	42	<5	<20	39	0.04	<10	56	<10	13	142
61	L23400N 4500E	5	0.8	0.99	<5	100	<5	0.14	<1	7	25	15	2.40	<10	0.19	131	1	0.01	11	360	16	<5	<20	2	0.12	<10	35	<10	1	27
62	L23400N 4525E	5	0.7	2.66	10	110	<5	0.23	<1	15	58	41	3.85	<10	0.62	414	2	0.01	38	510	26	<5	<20	2	0.14	<10	58	<10	<1	73
63	L23400N 4550E	5	0.5	0.52	<5	30	<5	0.03	<1	2	15	9	0.90	<10	0.09	68	<1	0.01	5	350	10	<5	<20	<1	0.02	<10	28	<10	<1	13
64	L23400N 4575E	5	0.5	2.46	5	80	<5	0.19	<1	10	40	22	3.00	<10	0.41	280	2	0.01	16	400	24	<5	<20	<1	0.11	<10	38	<10	4	34
65	L23400N 4600E	5	0.6	0.86	5	70	<5	0.29	<1	10	40	34	3.45	<10	0.44	393	<1	<0.01	16	420	24	<5	<20	<1	0.11	<10	38	<10	<1	41

Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
66	L23400N 4625E	5	0.9	1.93	<5	280	<5	0.32	<1	19	51	53	3.77	<10	0.46	493	3	0.01	26	460	24	<5	<20	8	0.12	<10	58	<10	14	61
67	L23400N 4650E	110	1.0	2.19	5	260	<5	0.94	<1	17	45	49	3.20	<10	0.42	1353	3	0.02	27	780	28	<5	<20	19	0.07	<10	72	<10	15	87
68	L23400N 4675E	5	1.1	2.35	<5	250	<5	1.17	<1	17	47	50	3.11	10	0.47	2250	3	0.02	27	980	26	<5	<20	26	0.05	<10	71	<10	24	79
69	L23400N 4700E	5	1.1	2.24	5	280	<5	0.66	<1	17	48	52	3.41	<10	0.41	864	2	0.02	28	520	28	<5	<20	17	0.09	<10	54	<10	20	71
70	L23400N 4725E	5	1.3	2.99	10	325	<5	0.96	<1	15	50	52	2.72	10	0.42	1661	3	0.02	32	1640	28	<5	<20	29	0.03	<10	71	<10	32	81
71	L23400N 4750E	15	1.0	0.98	<5	105	<5	0.13	<1	5	17	18	1.95	<10	0.11	61	1	0.01	7	290	18	<5	<20	4	0.07	<10	22	<10	6	19
72	L23400N 4775E	5	0.4	0.85	<5	70	<5	0.20	<1	9	34	16	2.59	<10	0.35	168	1	0.01	14	320	22	<5	<20	1	0.10	<10	48	<10	2	35
73	L23400N 4800E	<5	0.4	0.51	<5	50	<5	0.09	<1	6	18	13	1.50	<10	0.12	123	<1	0.01	6	250	18	<5	<20	<1	0.09	<10	19	<10	3	21
74	L23400N 4825E	<5	0.6	1.14	<5	95	<5	0.22	<1	11	41	22	2.95	<10	0.46	373	1	0.01	18	340	16	<5	<20	2	0.09	<10	43	<10	2	40
75	L23400N 4850E	<5	0.6	1.35	<5	90	5	0.20	<1	12	38	26	3.05	<10	0.43	439	2	0.01	19	390	18	<5	<20	2	0.09	<10	39	<10	3	39
76	L23400N 4875E	<5	0.5	1.82	<5	115	5	0.28	<1	19	59	31	3.42	<10	0.95	419	1	0.01	33	340	22	<5	<20	1	0.10	<10	38	<10	7	58
77	L23400N 4900E	<5	0.4	2.25	<5	160	10	0.27	<1	21	67	46	4.06	<10	0.95	481	1	0.01	36	310	26	<5	<20	7	0.14	<10	47	<10	10	62
78	L23400N 4925E	<5	0.5	1.37	<5	85	5	0.33	<1	14	49	18	3.88	<10	0.60	389	<1	0.01	17	270	16	<5	<20	3	0.15	<10	48	<10	2	42
79	L23400N 4950E	<5	0.5	1.52	<5	95	5	0.22	<1	16	48	23	3.44	<10	0.66	467	2	0.01	24	270	22	<5	<20	2	0.11	<10	42	<10	5	51
80	L23400N 4975E	5	0.4	2.27	<5	120	5	0.26	<1	20	71	31	4.60	<10	1.03	455	1	0.01	35	310	22	<5	<20	3	0.13	<10	44	<10	7	61
81	L23400N 5025E	725	0.8	0.58	70	30	<5	0.03	<1	5	4	29	2.86	<10	0.06	91	2	<0.01	23	420	64	<5	<20	<1	<0.01	<10	14	<10	<1	117
82	L23400N 5050E	>1000	>30	0.53	275	45	15	0.06	<1	14	3	111	6.37	<10	0.02	375	11	<0.01	40	1250	9570	20	<20	9	<0.01	<10	16	<10	<1	804
83	L23400N 5075E	>1000	>30	0.42	225	45	5	0.08	<1	12	2	149	5.28	<10	<0.01	424	9	<0.01	34	1200	7948	15	<20	14	<0.01	<10	13	<10	<1	650
84	L23400N 5100E	195	3.1	0.54	100	30	<5	0.06	<1	14	14	65	3.28	<10	<0.01	658	4	<0.01	23	510	420	<5	<20	5	0.01	<10	14	<10	<1	320
85	L23400N 5125E	15	1.7	0.64	10	160	5	0.18	<1	15	26	16	2.62	<10	0.25	4294	1	0.01	13	610	42	<5	<20	3	0.06	<10	43	<10	<1	84
86	L23400N 5150E	10	1.0	1.03	10	100	<5	0.27	<1	16	36	16	3.18	<10	0.44	1534	2	0.01	20	480	28	<5	<20	11	0.09	<10	39	<10	<1	92
87	L23400N 5175E	10	4.3	1.79	10	105	<5	1.28	4	8	18	41	2.01	<10	0.18	1990	<1	0.02	34	1330	32	<5	<20	133	0.02	<10	21	<10	16	70
88	L23400N 5200E	15	0.7	1.40	15	110	5	0.25	<1	16	50	33	3.44	<10	0.72	661	2	<0.01	34	590	30	<5	<20	6	0.08	<10	46	<10	3	108
89	L23400N 5225E	10	0.8	0.95	10	80	5	0.22	<1	13	38	16	2.97	<10	0.54	966	2	<0.01	21	360	26	<5	<20	6	0.09	<10	49	<10	<1	83
90	L23400N 5250E	10	1.0	0.54	<5	75	<5	0.09	<1	7	22	8	2.30	<10	0.16	413	1	0.01	8	840	16	<5	<20	<1	0.09	<10	47	<10	<1	33
91	L23400N 5275E	25	0.9	1.26	<5	70	<5	0.10	<1	11	39	14	3.04	<10	0.44	438	2	<0.01	19	470	22	<5	<20	<1	0.08	<10	52	<10	<1	48
92	L23400N 5300E	15	0.8	1.04	5	115	<5	0.17	<1	13	44	18	3.73	<10	0.44	388	2	<0.01	22	370	26	<5	<20	6	0.09	<10	50	<10	<1	58
93	L23400N 5325E	10	0.8	1.14	5	125	<5	0.26	<1	13	43	28	3.53	<10	0.45	407	1	0.01	25	500	26	<5	<20	12	0.07	<10	36	<10	<1	67
94	L23400N 5350E	10	1.0	1.63	5	235	<5	0.54	<1	17	53	45	3.43	<10	0.56	2628	<1	0.01	43	650	28	<5	<20	47	0.05	<10	51	<10	24	107
95	L23400N 5375E	10	2.3	2.24	10	230	<5	0.53	<1	20	59	69	3.75	<10	0.62	3040	<1	0.02	56	880	32	<5	<20	48	0.05	<10	55	<10	26	132
96	L23400N 5400E	5	1.2	0.91	5	145	<5	0.22	<1	10	33	33	3.28	<10	0.27	439	2	<0.01	25	510	24	<5	<20	12	0.04	<10	52	<10	<1	60
97	L23400N 5425E	5	2.2	1.69	5	205	<5	0.50	<1	21	57	66	3.99	<10	0.65	2661	1	0.01	66	830	30	<5	<20	44	0.04	<10	46	<10	12	161
98	L23400N 5450E	10	1.9	2.01	10	200	<5	0.62	1	19	53	73	3.42	<10	0.46	2636	1	0.01	64	1890	32	<5	<20	59	0.01	<10	53	<10	29	111
99	L23400N 5475E	15	1.4	1.81	10	180	<5	0.33	<1	20	59	43	3.74	<10	0.77	904	2	0.01	57	760	30	<5	<20	27	0.03	<10	55	<10	8	142
100	L23400N 5500E	10	1.1	1.19	5	210	<5	0.89	<1	15	38	31	2.95	<10	0.53	504	1	0.01	42	650	26	<5	<20	84	0.02	<10	37	<10	5	92

Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn	
QC DATA:																															
<i>Repeat:</i>																															
1	L22600N 5025E	5	0.7	0.69	<5	55	<5	0.14	<1	7	25	10	2.50	<10	0.15	326	1	0.01	9	410	14	<5	<20	1	0.14	<10	59	<10	<1	29	
10	L22600N 5250E	5	2.4	0.78	<5	215	<5	0.40	<1	12	32	17	2.78	<10	0.28	1656	<1	0.01	16	820	18	<5	<20	12	0.10	<10	64	<10	<1	76	
19	L22600N 5475E	5	0.9	2.09	10	200	<5	0.23	<1	25	72	44	4.42	<10	0.91	661	2	0.01	54	460	26	<5	<20	7	0.08	<10	72	<10	7	96	
28	L23300N 4675E	5	1.0	2.62	5	330	<5	0.56	<1	19	69	46	4.12	<10	0.73	622	4	0.02	45	690	26	<5	<20	19	0.08	<10	95	<10	9	98	
36	L23300N 4875E	5	0.8	1.60	<5	145	<5	0.16	<1	15	50	15	3.28	<10	0.65	561	2	0.01	22	270	18	<5	<20	4	0.14	<10	75	<10	1	50	
45	L23300N 5125E	15	0.9	0.41	10	60	<5	0.12	<1	6	15	16	2.81	<10	0.05	216	4	<0.01	14	630	26	<5	<20	4	0.07	<10	68	<10	<1	65	
54	L23300N 5350E	5	2.2	2.24	10	130	<5	0.11	<1	17	41	25	4.00	<10	0.36	1129	2	0.01	23	1080	28	<5	<20	1	0.06	<10	57	<10	<1	91	
63	L23400N 4550E	5	0.4	0.52	<5	35	<5	0.04	<1	2	16	9	0.90	<10	0.09	81	<1	0.01	6	370	10	<5	<20	<1	0.02	<10	28	<10	<1	13	
71	L23400N 4750E	<5	<0.2	1.08	<5	110	<5	0.14	<1	5	18	19	2.16	<10	0.10	60	1	0.01	8	320	20	<5	<20	2	0.06	<10	17	<10	8	21	
80	L23400N 4975E	10	<0.2	2.26	<5	115	10	0.31	<1	21	73	31	4.55	<10	1.11	480	<1	0.01	36	290	24	<5	<20	4	0.16	<10	47	<10	6	61	
89	L23400N 5225E	20	<0.2	0.93	5	70	<5	0.22	<1	14	37	16	2.94	<10	0.55	934	2	<0.01	23	360	24	<5	<20	6	0.08	<10	49	<10	<1	87	
<i>Standard:</i>																															
	GEO'04	140	1.6	1.63	50	140	<5	1.40	<1	17	60	88	3.90	<10	0.85	596	<1	0.03	26	630	24	<5	<20	54	0.11	<10	65	<10	8	76	
	GEO'04	135	1.5	1.60	50	135	<5	1.38	<1	17	58	88	3.83	<10	0.84	596	<1	0.03	26	640	22	<5	<20	59	0.11	<10	65	<10	8	74	
	GEO'04	140	1.6	1.52	45	140	<5	1.34	<1	17	58	84	3.78	<10	0.81	579	<1	0.03	26	660	22	<5	<20	58	0.11	<10	61	<10	8	73	

IJ/jm
#/1601/1600
(LS/04


ECO TECH LABORATORY LTD.
Jutta Jealouse
BC Certified Assayer

ECO TECH LABORATORY LTD.
10041 Dallas Drive
KAMLOOPS, B.C.
V2C 6T4

ICP CERTIFICATE OF ANALYSIS AK 2004-1602

NAVASOTA RESOURCES
#207 141 VICTORIA STREET
KAMLOOPS, BC
V2C 1Z5

Phone: 250-573-5700

Fax : 250-573-4557

No. of samples received: 100
Sample type: Soil
Project #: Not Indicated
Shipment #: Not Indicated

Values in ppm unless otherwise reported

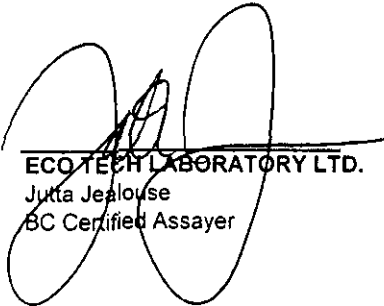
Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
1	L23500N 4500E	5	0.8	2.55	<5	225	5	0.16	<1	22	73	68	4.49	<10	0.68	466	3	0.01	40	460	34	<5	<20	5	0.15	<10	63	<10	15	72
2	L23500N 4525E	5	0.6	2.46	<5	190	<5	0.29	<1	22	61	40	3.62	<10	0.62	492	2	0.01	34	480	32	<5	<20	4	0.12	<10	57	<10	16	72
3	L23500N 4550E	<5	0.3	0.80	<5	80	5	0.11	<1	8	28	11	2.90	<10	0.18	276	2	0.01	11	350	18	<5	<20	<1	0.15	<10	47	<10	2	32
4	L23500N 4575E	15	0.2	2.49	<5	70	10	0.21	<1	17	61	25	4.77	<10	0.61	352	2	0.01	25	450	28	<5	<20	<1	0.22	<10	45	<10	8	60
5	L23500N 4600E	5	0.3	1.23	<5	65	10	0.16	<1	10	37	13	3.28	<10	0.36	221	1	0.01	15	370	20	<5	<20	<1	0.15	<10	49	<10	1	42
6	L23500N 4625E	5	0.4	1.17	<5	85	5	0.23	<1	14	43	13	3.45	<10	0.41	544	2	0.01	17	460	18	<5	<20	2	0.16	<10	50	<10	3	54
7	L23500N 4650E	<5	1.0	1.86	<5	230	10	0.28	<1	20	55	41	3.57	<10	0.56	1071	2	0.01	28	540	26	<5	<20	6	0.11	<10	68	<10	22	66
8	L23500N 4675E	<5	1.2	2.67	5	320	<5	0.46	<1	27	58	63	3.65	20	0.54	1437	3	0.01	35	840	30	<5	<20	14	0.07	<10	92	<10	38	86
9	L23500N 4700E	<5	0.5	1.88	<5	250	5	0.62	<1	16	59	30	3.93	<10	0.68	507	2	0.01	31	500	24	<5	<20	12	0.12	<10	60	<10	8	73
10	L23500N 4725E	<5	0.5	1.09	<5	80	<5	0.14	<1	8	20	20	2.60	<10	0.12	100	1	0.01	9	340	18	<5	<20	2	0.10	<10	21	<10	6	27
11	L23500N 4750E	20	0.2	2.25	5	100	5	0.29	<1	17	62	32	3.80	<10	0.87	310	1	0.01	32	320	24	<5	<20	1	0.16	<10	39	<10	7	55
12	L23500N 4775E	5	0.4	2.46	<5	110	5	0.22	<1	15	55	25	4.38	<10	0.58	335	2	0.01	24	480	26	<5	<20	2	0.17	<10	50	<10	4	59
13	L23500N 4800E	5	<0.2	2.18	<5	85	5	0.28	<1	19	67	28	4.22	<10	0.85	480	1	0.01	30	280	24	<5	<20	2	0.18	<10	38	<10	6	55
14	L23500N 4825E	<5	1.1	3.53	10	335	<5	0.68	<1	32	78	69	4.46	<10	0.83	963	2	0.01	56	950	36	<5	<20	20	0.06	<10	87	<10	24	118
15	L23500N 4850E	<5	0.3	1.70	<5	140	5	0.37	<1	19	67	26	4.90	<10	0.86	700	1	0.01	27	500	20	<5	<20	4	0.20	<10	43	<10	4	68
16	L23500N 4875E	5	<0.2	2.16	<5	65	10	0.44	<1	21	69	40	4.42	<10	1.10	436	<1	0.01	35	350	20	<5	<20	2	0.19	<10	35	<10	7	57
17	L23500N 4900E	5	0.5	2.39	<5	150	10	0.42	<1	28	64	34	3.95	<10	0.87	2169	3	0.01	31	460	24	<5	<20	9	0.10	<10	78	<10	13	71
18	L23500N 4925E	5	0.4	2.15	<5	265	<5	0.40	<1	26	52	55	4.60	<10	0.61	1416	2	0.01	42	780	26	<5	<20	17	0.05	<10	69	<10	7	165
19	L23500N 4950E	15	0.9	0.78	5	575	<5	1.35	<1	9	7	24	0.94	<10	0.10	2811	<1	0.05	19	1060	28	<5	<20	57	<0.01	<10	20	<10	20	119
20	L23500N 4975E	5	0.3	1.01	<5	75	10	0.11	<1	10	35	11	3.46	<10	0.32	436	2	0.01	13	340	18	<5	<20	1	0.14	<10	67	<10	<1	37
21	L23600N 4500E	10	0.4	2.68	<5	240	<5	0.18	<1	18	68	58	3.95	<10	0.60	698	2	0.02	37	530	32	<5	<20	4	0.07	<10	86	<10	21	76
22	L23600N 4525E	5	0.5	1.65	<5	115	10	0.28	<1	15	60	23	4.00	<10	0.70	323	2	0.01	27	310	22	<5	<20	5	0.15	<10	48	<10	3	58
23	L23600N 4550E	5	0.3	1.56	<5	80	10	0.14	<1	12	43	17	3.82	<10	0.40	273	2	0.01	18	430	22	<5	<20	<1	0.13	<10	48	<10	<1	48
24	L23600N 4575E	5	0.3	0.63	<5	80	<5	0.19	<1	7	19	9	2.19	<10	0.14	1009	<1	0.01	8	410	16	<5	<20	5	0.12	<10	23	<10	1	35
25	L23600N 4600E	5	<0.2	1.15	<5	65	10	0.20	<1	12	43	15	3.40	<10	0.44	336	1	0.01	19	370	20	<5	<20	1	0.15	<10	51	<10	3	44

N	OTA	DUR	ICP																	IFIC										IFAI										SIS /										04-1										E										ECH										DRA										LTD									
Et #	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn																																																																					
26	L23600N 4625E	15	<0.2	2.13	<5	75	5	0.32	<1	18	79	32	4.84	<10	0.84	456	2	0.01	37	700	24	<5	<20	3	0.11	<10	75	<10	2	72																																																																					
27	L23600N 4650E	5	0.2	2.16	<5	95	10	0.30	<1	18	63	25	4.03	<10	0.82	422	1	0.01	31	420	22	<5	<20	2	0.14	<10	51	<10	4	76																																																																					
28	L23600N 4675E	5	0.3	1.17	<5	105	<5	0.21	<1	14	35	17	3.15	<10	0.38	610	2	0.01	17	440	20	<5	<20	5	0.12	<10	47	<10	3	48																																																																					
29	L23600N 4700E	5	0.3	1.37	<5	190	10	0.37	<1	18	52	20	3.75	<10	0.67	710	2	0.01	24	340	22	<5	<20	8	0.14	<10	50	<10	3	61																																																																					
30	L23600N 4725E	<5	0.5	1.01	<5	190	<5	0.22	<1	21	25	21	2.44	<10	0.22	2610	2	0.01	15	420	20	<5	<20	6	0.13	<10	40	<10	8	57																																																																					
31	L23600N 4750E	<5	0.7	3.08	10	355	<5	0.81	<1	18	64	52	3.26	10	0.60	1549	3	0.02	41	1270	36	<5	<20	25	0.04	<10	88	<10	31	117																																																																					
32	L23600N 4775E	5	0.2	2.28	<5	165	10	0.48	<1	27	71	34	4.13	<10	1.15	527	3	0.01	40	370	26	<5	<20	8	0.16	<10	54	<10	11	68																																																																					
33	L23600N 4800E	<5	<0.2	2.31	<5	170	10	0.46	<1	27	72	35	4.21	<10	1.13	511	2	0.01	40	370	24	<5	<20	8	0.15	<10	56	<10	11	68																																																																					
34	L23600N 4825E	<5	0.6	2.00	<5	295	10	0.80	<1	15	53	31	3.30	<10	0.61	1079	3	0.01	32	490	28	<5	<20	24	0.08	<10	54	<10	18	116																																																																					
35	L23600N 4850E	55	0.3	0.77	<5	60	10	0.13	<1	7	19	12	2.38	<10	0.10	127	2	0.01	8	240	16	<5	<20	2	0.13	<10	37	<10	1	24																																																																					
36	L23600N 4875E	5	0.4	3.19	10	135	5	0.51	<1	26	64	62	3.60	<10	0.83	373	3	0.01	49	620	34	<5	<20	10	0.10	<10	50	<10	27	68																																																																					
37	L23600N 4900E	<5	0.4	0.76	<5	115	5	0.19	<1	8	26	14	2.38	<10	0.17	188	2	0.01	11	360	16	<5	<20	3	0.14	<10	44	<10	3	32																																																																					
38	L23600N 4925E	<5	0.3	2.69	5	120	15	0.21	<1	18	70	31	4.30	<10	0.88	371	3	0.01	34	510	36	<5	<20	5	0.20	<10	59	<10	6	64																																																																					
39	L23600N 4950E	<5	0.4	2.40	5	165	5	0.27	<1	25	58	34	4.05	<10	0.69	838	3	0.01	33	440	32	<5	<20	8	0.17	<10	65	<10	8	82																																																																					
40	L23600N 4975E	<5	0.4	1.69	<5	225	5	0.39	<1	17	45	23	3.33	<10	0.49	830	2	0.01	22	460	24	<5	<20	14	0.13	<10	51	<10	9	65																																																																					
41	L23600N 5025E	10	0.3	2.42	20	250	10	0.44	<1	29	77	44	4.47	<10	1.10	961	3	0.02	62	330	34	<5	<20	17	0.12	<10	63	<10	13	71																																																																					
42	L23600N 5050E	5	<0.2	2.60	<5	165	10	0.25	<1	20	77	40	4.45	<10	1.02	400	4	0.01	48	350	32	<5	<20	5	0.13	<10	70	<10	7	82																																																																					
43	L23600N 5075E	5	<0.2	0.71	<5	120	<5	0.12	<1	6	18	13	1.95	<10	0.15	255	2	0.02	9	510	24	<5	<20	4	0.07	<10	28	<10	<1	41																																																																					
44	L23600N 5100E	<5	0.5	1.59	5	160	5	0.20	<1	15	48	29	3.75	<10	0.47	562	3	0.02	26	420	26	<5	<20	7	0.13	<10	65	<10	7	72																																																																					
45	L23600N 5125E	<5	0.5	1.38	<5	235	5	0.63	<1	17	43	26	3.30	<10	0.50	1063	3	0.01	24	500	24	<5	<20	25	0.10	<10	64	<10	14	58																																																																					
46	L23600N 5150E	10	0.3	0.96	<5	170	5	0.29	<1	10	33	21	2.52	<10	0.30	462	2	0.02	18	410	26	<5	<20	14	0.07	<10	57	<10	3	47																																																																					
47	L23600N 5175E	5	0.2	0.74	<5	160	<5	0.20	<1	9	29	12	2.33	<10	0.30	374	2	0.01	13	660	18	<5	<20	4	0.10	<10	41	<10	1	42																																																																					
48	L23600N 5200E	5	0.2	1.06	<5	80	10	0.16	<1	11	38	12	3.23	<10	0.36	473	2	0.01	13	690	22	<5	<20	3	0.13	<10	56	<10	2	41																																																																					
49	L23600N 5225E	5	0.6	0.84	<5	105	10	0.20	<1	9	28	12	2.57	<10	0.26	450	2	0.01	12	740	22	<5	<20	6	0.12	<10	41	<10	<1	40																																																																					
50	L23600N 5250E	<5	0.7	0.73	<5	135	<5	0.10	<1	6	21	11	2.81	<10	0.07	599	2	0.02	7	840	18	<5	<20	4	0.08	<10	47	<10	<1	33																																																																					
51	L23600N 5275E	10	1.3	1.69	5	120	10	0.29	<1	15	55	21	3.84	<10	0.69	589	3	0.01	31	610	28	<5	<20	6	0.13	<10	51	<10	3	81																																																																					
52	L23600N 5300E	10	0.3	0.95	<5	165	5	0.22	<1	13	44	15	3.26	<10	0.54	475	2	0.01	25	470	20	<5	<20	4	0.13	<10	57	<10	<1	70																																																																					
53	L23600N 5325E	<5	0.9	0.55	<5	200	5	0.18	<1	6	23	17	2.03	<10	0.14	192	2	0.01	11	480	20	<5	<20	6	0.07	<10	50	<10	<1	43																																																																					
54	L23600N 5350E	<5	0.6	1.83	65	155	<5	1.60	<1	19	69	86	4.25	<10	0.92	652	<1	0.06	28	700	36	<5	<20	82	0.14	<10	90	<10	7	84																																																																					
55	L23600N 5375E	<5	1.1	0.42	<5	105	<5	0.11	<1	5	15	10	2.05	10	0.08	469	2	0.01	12	400	14	<5	<20	5	0.05	<10	57	<10	<1	39																																																																					
56	L23600N 5400E	<5	1.0	0.63	<5	65	5	0.11	<1	7	21	8	2.52	<10	0.13	153	2	0.01	11	310	20	<5	<20	4	0.11	<10	46	<10	2	32																																																																					
57	L23600N 5425E	<5	0.8	2.04	15	155	10	0.17	<1	19	49	29	4.03	10	0.50	558	5	0.01	37	500	40	<5	<20	7	0.07	<10	48	<10	2	99																																																																					
58	L23600N 5450E	<5	0.9	2.05	15	170	10	0.15	<1	18	47	28	4.02	<10	0.45	746	3	0.01	34	520	36	<5	<20	5	0.07	<10	50	<10	<1	97																																																																					
59	L23600N 5475E	30	<0.2	1.27	10	520	5	0.18	<1	18	43	42	3.88	10	0.65	649	3	<0.01	50	510	26	<5	<20	12	0.04	<10	41	<10	3	88																																																																					
60	L23600N 5500E	<5	<0.2	1.21	10	445	<5	0.18	<1	17	42	45	3.58	<10	0.66	699	3	<0.01	50	530	24	<5	<20	14	0.04	<10	39	<10	3	81																																																																					
61	L23800N 4500E	<5	0.7	3.06	50	775	<5	0.64	<1	31	90	101	4.51	20	0.90	1708	4	0.02	54	870	36	<5	<20	33	0.09	<10	96	<10	98	114																																																																					
62	L23800N 4525E	<5	0.8	2.29	25	775	<5	0.92	<1	17	64	76	2.98	20	0.61	1050	2	0.02	37	1000	34	<5	<20	53	0.06	<10	60	<10	101	71																																																																					
63	L23800N 4550E	<5	0.7	2.81	25	410	10	0.54	<1	24	84	76	4.53	<10	0.82	875	3	0.02	52	570	40	<5	<20	18	0.12	<10	77	<10	25	97																																																																					
64	L23800N 4575E	<5	0.4	1.21	<5	100	<5	0.22	<1	9	25	20	2.10	<10	0.19	307	2	0.02	11	320	22	<5	<20	6	0.14	<10	23	<10	9	29																																																																					
65	L23800N 4600E	<5	1.0	3.70	25	395	<5	0.77	<1	26	83	84	4.42	10	0.72	3314	3	0.02	54	1060	46	<5	<20	20	0.07	<10	107	<10	35	113																																																																					

Et #	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
66	L23800N 4625E	<5	0.8	2.50	15	210	5	0.86	<1	22	45	46	3.18	10	0.36	3479	3	0.02	26	1120	34	<5	<20	19	0.06	<10	84	<10	20	73
67	L23800N 4650E	<5	0.5	3.28	35	220	<5	1.08	<1	21	59	56	3.81	<10	0.56	1208	4	0.02	38	850	40	<5	<20	19	0.12	<10	61	<10	24	82
68	L23800N 4675E	<5	0.3	2.35	10	185	<5	1.13	<1	18	54	51	3.81	<10	0.50	398	3	0.02	32	810	30	<5	<20	19	0.09	<10	69	<10	13	75
69	L23800N 4700E	<5	<0.2	2.15	15	160	5	0.90	<1	16	46	30	3.32	<10	0.48	542	3	0.02	23	680	28	<5	<20	17	0.06	<10	57	<10	14	72
70	L23800N 4725E	<5	1.0	3.88	20	320	5	0.74	<1	33	82	88	4.67	<10	0.78	1146	4	0.02	56	1000	46	<5	<20	22	0.10	<10	89	<10	19	115
71	L23800N 4750E	5	0.5	1.15	<5	170	5	0.46	<1	20	40	31	3.04	<10	0.38	722	2	0.01	19	500	20	<5	<20	13	0.10	<10	55	<10	6	51
72	L23800N 4775E	10	0.4	1.20	<5	90	5	0.27	<1	13	31	30	2.54	<10	0.28	344	2	0.01	16	380	22	<5	<20	6	0.08	<10	39	<10	8	36
73	L23800N 4800E	5	0.7	1.97	<5	180	10	0.37	<1	25	58	52	3.61	<10	0.67	808	3	0.01	31	520	24	<5	<20	10	0.07	<10	60	<10	15	66
74	L23800N 4825E	5	0.5	1.35	<5	100	10	0.26	<1	14	40	25	2.98	<10	0.37	691	3	0.01	17	400	22	<5	<20	4	0.12	<10	41	<10	9	43
75	L23800N 4850E	5	0.8	2.67	5	350	<5	0.61	<1	19	55	52	2.83	10	0.52	2143	2	0.02	35	1380	34	<5	<20	26	0.02	<10	76	<10	29	80
76	L23800N 4875E	5	0.7	2.10	5	300	<5	1.04	<1	8	40	39	1.55	10	0.39	278	1	0.01	28	1090	30	<5	<20	37	0.02	<10	42	<10	27	89
77	L23800N 4900E	5	0.2	0.48	<5	75	<5	0.20	<1	5	14	8	1.74	<10	0.08	241	1	0.01	5	280	14	<5	<20	4	0.11	<10	18	<10	2	34
78	L23800N 4925E	5	0.2	0.48	<5	65	5	0.21	<1	5	14	7	1.79	<10	0.08	237	<1	0.01	5	250	12	<5	<20	4	0.10	<10	10	<10	3	37
79	L23800N 4950E	<5	0.7	0.68	<5	70	5	0.14	<1	8	29	9	2.06	<10	0.25	508	1	0.01	12	300	18	<5	<20	1	0.09	<10	41	<10	2	31
80	L23800N 4975E	<5	0.4	2.00	15	95	5	0.19	<1	19	59	34	4.20	<10	0.72	483	3	0.01	39	500	30	<5	<20	3	0.09	<10	51	<10	5	78
81	L23800N 5025E	<5	0.4	2.03	10	175	<5	0.50	<1	21	60	32	3.63	<10	0.72	1576	3	0.01	42	650	28	<5	<20	40	0.05	<10	66	<10	7	106
82	L23800N 5050E	5	1.2	1.80	10	210	<5	0.78	2	19	33	32	3.25	<10	0.53	1998	2	0.01	35	1020	112	<5	<20	73	0.04	<10	50	<10	9	263
83	L23800N 5075E	5	0.9	1.97	10	190	<5	0.71	2	22	39	37	3.62	<10	0.68	1671	3	0.02	43	1030	110	<5	<20	65	0.05	<10	59	<10	9	297
84	L23800N 5100E	5	0.6	0.60	10	85	5	0.08	<1	13	23	14	3.41	<10	0.12	1128	3	0.01	14	700	34	<5	<20	2	0.06	<10	58	<10	<1	67
85	L23800N 5125E	5	1.2	1.15	5	90	<5	0.42	<1	13	19	31	3.33	<10	0.14	361	3	0.01	25	640	34	<5	<20	33	0.03	<10	45	<10	6	62
86	L23800N 5150E	5	0.9	1.10	5	200	5	0.17	<1	15	38	26	3.60	<10	0.32	879	3	0.01	28	570	28	<5	<20	10	0.05	<10	61	<10	<1	96
87	L23800N 5175E	<5	0.7	0.92	5	195	5	0.18	<1	12	36	23	3.46	<10	0.32	659	3	<0.01	27	510	26	<5	<20	7	0.05	<10	65	<10	<1	91
88	L23800N 5200E	<5	1.1	0.59	5	95	5	0.11	<1	7	21	15	3.21	<10	0.14	456	3	0.01	15	1310	24	<5	<20	2	0.04	<10	50	<10	<1	62
89	L23800N 5225E	<5	1.0	1.22	15	200	<5	0.67	<1	17	31	26	3.74	<10	0.22	4343	2	0.01	31	850	34	<5	<20	47	0.03	<10	45	<10	2	173
90	L23800N 5250E	<5	0.3	1.25	20	135	<5	0.27	<1	21	46	38	4.00	<10	0.60	494	3	0.01	57	360	30	<5	<20	18	0.02	<10	40	<10	<1	93
91	L23800N 5275E	<5	0.5	1.72	10	160	<5	0.40	<1	17	59	24	3.92	<10	0.85	327	2	0.02	69	380	34	<5	<20	22	0.05	<10	46	<10	5	213
92	L23800N 5300E	<5	0.2	1.31	20	120	<5	0.10	<1	17	39	46	4.53	<10	0.47	278	4	<0.01	50	440	34	<5	<20	2	0.03	<10	43	<10	<1	119
93	L23800N 5325E	<5	0.4	1.43	10	110	<5	0.13	<1	20	46	33	4.10	<10	0.59	961	3	<0.01	41	490	34	<5	<20	3	0.05	<10	49	<10	<1	125
94	L23800N 5350E	<5	0.3	1.33	10	180	5	0.22	<1	20	48	40	3.61	<10	0.73	445	3	0.01	48	630	28	<5	<20	8	0.04	<10	41	<10	4	97
95	L23800N 5375E	<5	0.4	1.23	<5	115	10	0.16	<1	12	44	21	3.77	<10	0.47	361	3	0.01	23	510	24	<5	<20	2	0.10	<10	56	<10	<1	65
96	L23800N 5400E	<5	0.4	0.69	<5	80	5	0.15	<1	9	29	14	3.07	<10	0.21	242	3	0.01	14	630	20	<5	<20	3	0.09	<10	57	<10	<1	48
97	L23800N 5425E	<5	0.5	1.02	10	65	<5	0.08	<1	10	30	18	3.36	<10	0.36	359	3	<0.01	25	500	28	<5	<20	<1	0.04	<10	56	<10	<1	83
98	L23800N 5450E	<5	0.4	1.71	10	125	<5	0.16	<1	15	46	31	3.99	<10	0.62	340	3	<0.01	48	490	32	<5	<20	6	0.03	<10	49	<10	<1	123
99	L23800N 5475E	<5	0.4	0.41	<5	115	5	0.15	<1	6	18	9	1.81	<10	0.11	465	2	<0.01	9	610	16	<5	<20	4	0.03	<10	40	<10	<1	39
100	L23800N 5500E	<5	0.5	1.18	10	305	<5	0.41	<1	14	35	39	3.32	<10	0.41	980	3	<0.01	40	820	28	<5	<20	33	0.02	<10	45	<10	16	86

Et #	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn	
QC DATA:																															
Repeat:																															
1	L23500N 4500E	5	0.7	2.47	<5	215	5	0.15	<1	21	71	64	4.37	<10	0.65	433	2	0.01	38	440	32	<5	<20	2	0.14	<10	65	<10	14	68	
10	L23500N 4725E	5	0.4	1.07	<5	75	5	0.14	<1	7	20	20	2.54	<10	0.12	102	2	0.01	10	320	18	<5	<20	3	0.10	<10	27	<10	6	27	
19	L23500N 4950E	<5	0.7	0.79	10	530	<5	1.33	<1	9	8	23	1.00	<10	0.10	2799	<1	0.01	18	1080	22	<5	<20	57	<0.01	<10	22	<10	18	113	
28	L23600N 4675E	<5	0.3	1.07	<5	95	10	0.18	<1	13	32	16	3.01	<10	0.35	566	2	0.01	15	410	20	<5	<20	4	0.12	<10	50	<10	3	46	
36	L23600N 4875E	5	0.4	3.17	10	135	5	0.48	<1	26	60	61	3.46	<10	0.73	371	2	0.01	46	640	32	<5	<20	10	0.12	<10	49	<10	27	68	
45	L23600N 5125E	<5	0.5	1.34	<5	230	10	0.61	<1	16	43	25	3.30	<10	0.50	1079	2	0.01	23	520	26	<5	<20	24	0.10	<10	68	<10	13	59	
54	L23600N 5350E	10	0.7	1.81	5	115	10	0.16	<1	12	45	18	3.42	<10	0.35	340	3	0.01	25	360	32	<5	<20	5	0.09	<10	59	<10	4	57	
63	L23800N 4550E	<5	0.7	3.00	25	420	5	0.56	<1	27	89	79	4.76	<10	0.88	946	3	0.02	55	600	42	<5	<20	17	0.12	<10	77	<10	26	99	
71	L23800N 4750E	<5	0.4	1.16	<5	170	5	0.48	<1	21	40	32	3.02	<10	0.39	735	3	0.01	20	530	20	<5	<20	13	0.08	<10	53	<10	5	52	
80	L23800N 4975E	<5	0.5	1.96	15	90	10	0.19	<1	20	60	35	4.50	<10	0.78	490	3	0.01	42	460	30	<5	<20	2	0.09	<10	52	<10	4	80	
89	L23800N 5225E	<5	1.0	1.21	15	190	<5	0.66	<1	16	31	27	3.83	<10	0.22	4072	2	0.01	31	910	34	<5	<20	46	0.03	<10	44	<10	3	174	
98	L23800N 5450E	<5	0.3	1.74	15	125	<5	0.15	<1	15	45	31	4.00	<10	0.63	342	3	<0.01	48	490	32	<5	<20	5	0.03	<10	47	<10	<1	126	
Standard:																															
	GEO'04	140	1.5	1.47	45	135	<5	1.34	<1	17	56	84	3.76	<10	0.80	570	<1	0.02	24	630	22	<5	<20	56	0.11	<10	70	<10	7	71	
	GEO'04	140	1.5	1.67	45	150	5	1.43	<1	18	63	86	4.01	<10	0.85	607	<1	0.03	27	640	24	<5	<20	64	0.11	<10	67	<10	7	74	
	GEO'04	140	1.5	1.52	50	140	<5	1.36	<1	17	57	87	3.81	<10	0.81	578	<1	0.03	26	640	22	<5	<20	56	0.11	<10	67	<10	7	71	

IJ/jm
 1/1602/1665
 (LS/04


 ECO TECH LABORATORY LTD.
 Jutta Jealousse
 BC Certified Assayer

ECO TECH LABORATORY LTD.
10041 Dallas Drive
KAMLOOPS, B.C.
V2C 6T4

ICP CERTIFICATE OF ANALYSIS AK 2004-1601

NAVASOTA RESOURCES
#207 141 VICTORIA STREET
KAMLOOPS, BC
V2C 1Z5

Phone: 250-573-5700
Fax : 250-573-4557

No. of samples received: 60
Sample type: Soil
Project #: Not Indicated
Shipment #: Not Indicated

Values in ppm unless otherwise reported

Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
1	L22800N 5025E	<5	0.5	0.84	<5	95	<5	0.19	<1	9	33	12	2.87	<10	0.29	261	1	0.01	14	220	18	<5	<20	5	0.19	<10	67	<10	2	31
2	L22800N 5050E	5	1.0	1.73	<5	130	<5	0.36	<1	18	45	38	3.58	<10	0.56	842	3	0.01	26	420	28	<5	<20	32	0.10	<10	88	<10	6	94
3	L22800N 5075E	<5	1.2	1.20	<5	90	5	0.24	<1	14	38	17	3.04	<10	0.55	489	1	0.01	19	390	18	<5	<20	2	0.16	<10	61	<10	<1	51
4	L22800N 5100E	<5	1.1	1.30	<5	65	5	0.26	<1	12	43	14	3.31	<10	0.56	299	1	0.01	19	270	16	<5	<20	<1	0.21	<10	69	<10	<1	46
5	L22800N 5125E	<5	0.8	0.67	<5	90	<5	0.16	<1	12	16	104	9.15	<10	0.13	291	9	<0.01	53	1190	20	<5	<20	4	0.05	<10	60	<10	<1	314
6	L22800N 5150E	5	0.8	1.08	<5	95	<5	0.13	<1	8	28	32	3.32	<10	0.29	162	3	<0.01	21	360	30	<5	<20	5	0.11	<10	62	<10	<1	68
7	L22800N 5175E	35	1.3	1.66	55	105	<5	0.14	<1	28	30	46	4.44	<10	0.39	508	4	<0.01	91	350	62	<5	<20	7	0.07	<10	41	<10	6	241
8	L22800N 5200E	5	0.7	1.11	10	180	<5	0.38	<1	18	36	49	3.44	<10	0.38	833	2	0.01	30	550	104	<5	<20	29	0.12	<10	65	<10	2	120
9	L22800N 5225E	5	0.8	1.28	15	170	<5	0.24	<1	19	41	59	4.23	<10	0.30	1244	4	0.01	37	690	58	<5	<20	14	0.08	<10	81	<10	8	118
10	L22800N 5250E	10	0.7	0.92	<5	120	<5	0.40	<1	13	38	28	3.18	<10	0.38	904	2	0.01	23	670	26	<5	<20	29	0.07	<10	77	<10	<1	70
11	L22800N 5275E	5	0.7	1.15	<5	95	<5	0.18	<1	13	43	30	3.99	<10	0.41	704	3	0.01	23	650	22	<5	<20	3	0.10	<10	94	<10	<1	74
12	L22800N 5300E	5	0.9	0.79	<5	120	5	0.13	<1	9	28	19	2.93	<10	0.20	403	2	0.01	12	450	16	<5	<20	3	0.10	<10	73	<10	<1	61
13	L22800N 5325E	5	0.7	0.66	<5	350	<5	0.45	<1	13	27	15	2.67	<10	0.27	2686	<1	0.01	17	560	26	<5	<20	17	0.09	<10	57	<10	<1	100
14	L22800N 5350E	5	0.6	1.92	10	165	5	0.33	<1	17	64	27	4.79	<10	0.90	403	3	0.01	37	800	24	<5	<20	13	0.12	<10	89	<10	<1	112
15	L22800N 5375E	5	0.8	0.90	<5	220	<5	0.20	<1	10	28	18	3.34	<10	0.25	1036	2	0.01	16	740	18	<5	<20	6	0.10	<10	65	<10	<1	74
16	L22800N 5400E	5	1.1	1.23	<5	270	<5	0.88	<1	13	40	61	2.77	<10	0.57	427	2	0.01	44	480	24	<5	<20	87	0.08	<10	47	<10	14	69
17	L22800N 5425E	5	0.9	3.02	15	565	<5	0.85	2	28	91	164	4.77	10	0.78	1513	4	0.02	106	1260	50	<5	<20	90	0.04	<10	88	<10	84	145
18	L22800N 5450E	5	0.5	2.15	15	415	<5	1.00	<1	17	62	84	3.28	10	0.74	789	3	0.01	75	880	36	<5	<20	99	0.03	<10	54	<10	76	97
19	L22800N 5475E	10	1.7	2.57	15	455	<5	0.63	<1	25	87	98	5.04	<10	0.94	980	4	0.01	97	750	44	<5	<20	64	0.05	<10	82	<10	23	140
20	L22800N 5500E	5	1.3	2.91	20	590	<5	0.92	<1	26	89	122	4.95	<10	0.86	1272	4	0.01	113	1380	48	<5	<20	99	0.03	<10	86	<10	53	165
21	L23000N 5025E	5	0.6	1.21	<5	85	10	0.20	<1	14	46	20	3.81	<10	0.51	292	2	0.01	24	240	20	<5	<20	5	0.23	<10	70	<10	2	62
22	L23000N 5050E	5	0.8	1.13	<5	60	5	0.27	<1	13	45	14	2.99	<10	0.65	221	<1	0.01	21	290	18	<5	<20	<1	0.20	<10	55	<10	6	38
23	L23000N 5075E	5	0.7	3.12	<5	100	<5	0.27	<1	19	62	28	4.24	<10	0.76	520	2	0.01	28	580	26	<5	<20	3	0.15	<10	35	<10	7	78
24	L23000N 5100E	5	0.7	0.85	<5	65	<5	0.06	<1	5	17	13	2.54	<10	0.07	127	2	0.01	9	460	24	<5	<20	2	0.07	<10	30	<10	<1	29
25	L23000N 5125E	5	1.1	1.79	<5	105	10	0.22	<1	14	54	21	4.90	<10	0.48	293	2	0.01	23	520	34	<5	<20	11	0.20	<10	45	<10	6	87
26	L23000N 5150E	5	0.9	0.54	40	325	<5	0.40	1	15	9	59	5.57	<10	0.09	3804	3	0.01	75	1050	30	<5	<20	52	<0.01	<10	39	<10	1	377
27	L23000N 5175E	<5	3.9	3.07	15	365	<5	0.94	7	11	20	60	1.08	20	0.21	2464	<1	0.02	43	2080	52	<5	<20	131	<0.01	<10	25	<10	57	237
28	L23000N 5200E	5	2.3	2.11	15	270	<5	0.54	6	18	29	66	2.54	10	0.32	2051	3	0.01	53	1430	48	<5	<20	71	0.01	<10	53	<10	34	264
29	L23000N 5225E	5	1.9	1.95	10	275	<5	0.53	5	21	34	69	2.93	10	0.40	2050	2	0.01	51	920	44	<5	<20	66	0.03	<10	52	<10	36	246
30	L23000N 5250E	5	1.2	1.82	5	205	5	0.39	2	21	48	55	4.07	<10	0.49	763	2	0.01	44	640	36	<5	<20	48	0.08	<10	71	<10	17	137

Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Z
31	L23000N 5275E	5	0.7	1.34	<5	230	5	0.30	<1	19	46	32	3.92	<10	0.58	817	2	0.01	31	450	30	<5	<20	18	0.11	<10	71	<10	1	10
32	L23000N 5300E	5	0.7	1.42	<5	205	<5	0.23	<1	15	45	23	4.01	<10	0.52	670	2	0.01	30	410	28	<5	<20	18	0.08	<10	73	<10	<1	9
33	L23000N 5325E	5	1.0	1.11	<5	205	<5	0.25	<1	20	35	25	3.41	<10	0.33	1601	2	0.01	26	820	34	<5	<20	20	0.05	<10	52	<10	<1	10
34	L23000N 5350E	5	1.7	1.76	5	175	<5	0.29	<1	22	46	61	3.61	<10	0.45	1015	2	0.01	36	510	38	<5	<20	30	0.07	<10	58	<10	18	9
35	L23000N 5375E	5	0.8	1.88	10	175	<5	0.32	<1	25	61	44	4.25	<10	0.89	695	2	0.01	59	530	30	<5	<20	23	0.05	<10	60	<10	6	9
36	L23000N 5400E	15	<0.2	1.53	15	175	10	0.20	<1	20	50	32	4.01	<10	0.62	862	3	<0.01	44	630	34	<5	<20	11	0.03	<10	58	<10	<1	10
37	L23000N 5425E	<5	0.4	0.93	5	120	<5	0.13	<1	13	36	24	3.34	<10	0.32	661	3	<0.01	23	520	24	<5	<20	8	0.03	<10	62	<10	<1	7
38	L23000N 5450E	5	1.5	2.50	10	270	<5	0.47	<1	25	71	88	4.67	<10	0.79	1091	2	0.02	60	760	44	<5	<20	43	0.05	<10	61	<10	19	12
39	L23000N 5475E	5	0.7	1.39	10	130	5	0.25	<1	15	43	48	3.74	<10	0.43	449	3	0.01	36	660	30	<5	<20	23	0.04	<10	50	<10	<1	7
40	L23000N 5500E	90	1.2	2.40	15	200	<5	0.25	<1	29	72	76	5.06	<10	0.75	1063	4	0.01	75	550	38	<5	<20	21	0.03	<10	65	<10	15	11
41	L23500N 5025E	15	<0.2	1.96	5	135	<5	0.22	<1	20	65	32	3.75	<10	0.92	513	2	0.01	39	350	28	<5	<20	5	0.09	<10	49	<10	6	6
42	L23500N 5050E	5	0.5	0.72	<5	115	5	0.16	<1	11	33	14	2.70	<10	0.31	887	1	0.01	15	530	26	<5	<20	3	0.06	<10	48	<10	<1	5
43	L23500N 5075E	15	<0.2	2.10	<5	145	5	0.34	<1	24	72	49	4.20	<10	1.24	528	1	<0.01	48	500	28	<5	<20	4	0.11	<10	45	<10	7	6
44	L23500N 5100E	40	0.3	0.59	<5	135	5	0.25	<1	8	23	14	2.26	<10	0.18	331	2	0.01	11	270	62	<5	<20	11	0.07	<10	49	<10	3	4
45	L23500N 5125E	5	<0.2	0.23	<5	65	<5	0.06	<1	2	7	5	0.62	<10	0.04	45	<1	0.01	5	240	8	<5	<20	3	0.02	<10	16	<10	<1	1
46	L23500N 5150E	10	0.2	1.33	10	205	<5	0.32	1	19	60	41	3.34	<10	0.92	524	1	0.02	43	660	36	<5	<20	28	0.05	<10	50	<10	10	23
47	L23500N 5175E	5	0.2	0.44	<5	70	<5	0.07	<1	4	16	9	1.61	<10	0.11	81	1	0.01	8	370	88	<5	<20	2	0.05	<10	27	<10	<1	2
48	L23500N 5200E	10	0.2	0.28	<5	40	<5	0.05	<1	2	10	4	0.53	<10	0.04	32	<1	0.01	4	230	18	<5	<20	<1	0.06	<10	5	<10	2	1
49	L23500N 5225E	<5	0.3	0.35	<5	70	<5	0.07	<1	4	15	7	1.24	<10	0.08	69	1	0.01	7	270	16	<5	<20	<1	0.05	<10	29	<10	<1	2
50	L23500N 5250E	5	<0.2	0.24	<5	55	<5	0.08	<1	4	15	6	0.99	<10	0.06	56	<1	0.01	5	210	12	<5	<20	<1	0.06	<10	26	<10	<1	1
51	L23500N 5275E	5	0.6	1.10	<5	95	5	0.14	<1	13	38	12	4.01	<10	0.42	326	2	0.01	16	380	22	<5	<20	2	0.16	<10	45	<10	1	5
52	L23500N 5300E	5	<0.2	1.63	<5	95	10	0.31	<1	19	55	23	3.55	<10	0.97	412	<1	<0.01	37	400	24	<5	<20	4	0.13	<10	32	<10	7	6
53	L23500N 5325E	5	0.7	0.93	<5	140	5	0.13	<1	11	32	12	3.32	<10	0.31	1260	2	0.01	16	550	22	<5	<20	2	0.09	<10	65	<10	<1	5
54	L23500N 5350E	5	0.7	1.24	<5	115	<5	0.27	<1	13	38	35	3.52	<10	0.44	404	3	0.01	27	470	26	<5	<20	18	0.07	<10	52	<10	1	6
55	L23500N 5375E	5	1.4	1.52	<5	220	<5	0.64	2	11	35	46	2.79	<10	0.42	766	2	0.01	35	630	30	<5	<20	63	0.06	<10	45	<10	17	9
56	L23500N 5400E	5	1.0	1.59	5	200	<5	0.52	<1	16	47	38	3.25	<10	0.50	1914	2	0.01	39	830	28	<5	<20	45	0.04	<10	57	<10	10	11
57	L23500N 5425E	5	0.8	1.33	5	155	<5	0.20	<1	14	40	34	3.49	<10	0.49	757	3	0.01	29	730	28	<5	<20	7	0.07	<10	56	<10	2	7
58	L23500N 5450E	5	1.0	1.29	5	135	<5	0.39	<1	13	34	36	3.32	<10	0.34	1259	3	0.01	31	730	28	<5	<20	34	0.04	<10	50	<10	3	8
59	L23500N 5475E	5	1.3	1.49	5	210	<5	0.68	<1	16	34	42	3.13	<10	0.37	1580	3	0.01	37	1070	30	<5	<20	63	0.02	<10	51	<10	7	10
60	L23500N 5500E	5	1.7	1.43	10	115	<5	0.14	<1	11	33	33	4.22	<10	0.26	292	4	<0.01	26	750	32	<5	<20	9	0.04	<10	57	<10	<1	6

QC DATA:

Repeat:

1	L22800N 5025E	5	0.5	0.93	<5	95	5	0.21	<1	10	35	13	3.03	<10	0.32	297	2	0.01	15	260	18	<5	<20	4	0.20	<10	66	<10	1	40
10	L22800N 5250E	20	0.6	0.98	<5	110	<5	0.38	<1	14	40	26	3.22	<10	0.38	880	2	0.01	24	660	24	<5	<20	28	0.09	<10	72	<10	1	73
19	L22800N 5475E	5	2.0	2.72	15	490	<5	0.70	<1	26	85	102	5.10	<10	0.96	1049	2	0.02	97	890	48	<5	<20	73	0.05	<10	74	<10	27	149
28	L23000N 5200E	5	2.1	2.64	15	260	<5	0.51	5	19	29	60	2.72	10	0.35	1941	3	0.01	54	1340	48	<5	<20	65	0.02	<10	53	<10	32	270
36	L23000N 5400E	10	<0.2	1.61	15	170	<5	0.19	<1	20	53	34	4.12	<10	0.67	811	2	0.01	47	600	32	<5	<20	9	0.03	<10	60	<10	<1	104
45	L23500N 5125E	<0.2	0.22	<5	55	<5	0.06	<1	2	7	5	0.64	<10	0.03	51	<1	0.01	5	210	8	<5	<20	3	0.02	<10	18	<10	<1	15	
46	L23500N 5150E	15																												
54	L23500N 5350E	10	0.7	1.24	<5	115	5	0.26	<1	13	39	34	3.46	<10	0.43	410	3	0.01	29	500	24	<5	<20	18	0.07	<10	54	<10	<1	68

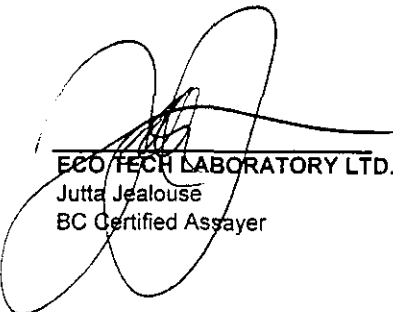
Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Z
-------	-------	---------	----	------	----	----	----	------	----	----	----	----	------	----	------	----	----	------	----	---	----	----	----	----	------	---	---	---	---	---

QC DATA:

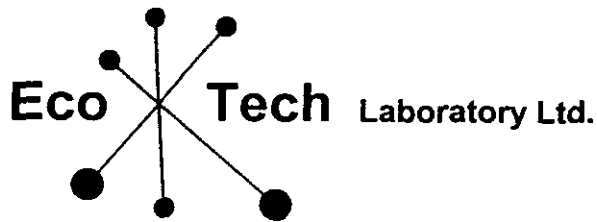
Standard:

GEO'04		135	1.6	1.59	55	150	<5	1.37	<1	17	58	88	3.84	<10	0.83	620	<1	0.03	26	680	20	<5	<20	52	0.07	<10	60	<10	6
GEO'04		130	1.4	1.49	50	140	<5	1.32	<1	17	57	86	3.75	<10	0.79	569	<1	0.03	25	630	22	<5	<20	54	0.07	<10	60	<10	10

JJ/jm
df/1601/1602
XLS/04



ECO TECH LABORATORY LTD.
Jutta Jealous
BC Certified Assayer



ASSAYING
GEOCHEMISTRY
ANALYTICAL CHEMISTRY
ENVIRONMENTAL TESTING

10041 Dallas Drive, Kamloops, BC V2C 6T4
Phone (250) 573-5700 Fax (250) 573-4557
E-mail: info@ecotechlab.com
www.ecotechlab.com

CERTIFICATE OF ASSAY AK 2005-003

NAVASOTA RESOURCES
#207 141 VICTORIA STREET
KAMLOOPS, BC
V2C 1Z5

13-Jan-05

No. of samples received: 17
Sample type: Core
Project #: Not Indicated
Shipment #: Not Indicated
Samples submitted by: R. Whiteaker

ET #.	Tag #	Au (g/t)	Au (oz/t)
1	22571	0.39	0.011
2	22572	0.03	0.001
3	22573	0.03	0.001
4	22574	<0.03	<0.001
5	22575	<0.03	<0.001
6	22576	<0.03	<0.001
7	22577	0.05	0.001
8	22578	0.35	0.010
9	22579	0.13	0.004
10	22580	<0.03	<0.001
11	22581	0.03	0.001
12	22582	0.12	0.003
13	22583	0.05	0.001
14	22584	<0.03	<0.001
15	22585	0.05	0.001
16	22586	0.04	0.001
17	22587	0.03	0.001

QC DATA:

Resplit:

1	22571	0.39	0.011
---	-------	------	-------

Jutta Jealous
ECO TECH LABORATORY LTD.
 Jutta Jealous
 B.C. Certified Assayer

ET #.	Tag #	Au (g/t)	Au (oz/t)
Repeat:			
1	22571	0.40	0.012
8	22578	0.32	0.009
Standard:			
OX123		1.86	0.054

JJ/jm
XLS/05

Jutta Jealouse
ECO TECH LABORATORY LTD.
 Jutta Jealouse
 B.C. Certified Assayer

ECO TECH LABORATORY LTD.
10041 Dallas Drive
KAMLOOPS, B.C.
V2C 6T4

ICP CERTIFICATE OF ANALYSIS AK 2005-003

NAVASOTA RESOURCES
#207 141 VICTORIA STREET
KAMLOOPS, BC
V2C 1Z5

Attention: Chris Wild

Phone: 250-573-5700
Fax : 250-573-4557

No. of samples received: 17
Sample type: Core
Project #: Not Indicated
Shipment #: Not Indicated
Samples submitted by: R. Whiteaker

Values in ppm unless otherwise reported

Et #.	Tag #	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
1	22571	0.3	0.19	20	50	<5	2.23	<1	18	62	31	5.61	<10	1.56	608	4	0.02	62	760	14	<5	<20	155	<0.01	<10	7	<10	<1	99
2	22572	<0.2	0.25	20	55	5	1.31	<1	23	41	65	5.69	<10	1.45	456	3	0.03	81	1020	16	<5	<20	103	<0.01	<10	8	<10	<1	84
3	22573	0.2	0.25	55	60	<5	0.65	<1	15	73	81	4.56	<10	1.22	362	4	0.02	70	600	26	<5	<20	58	<0.01	<10	7	<10	<1	71
4	22574	<0.2	0.20	85	50	<5	0.64	<1	12	116	51	3.17	<10	0.90	510	2	0.02	65	260	10	<5	<20	54	<0.01	<10	5	<10	<1	43
5	22575	<0.2	0.27	55	40	<5	0.73	<1	14	97	38	4.32	<10	1.13	527	4	0.01	53	310	10	<5	<20	67	<0.01	<10	5	<10	<1	55
6	22576	<0.2	0.31	40	65	<5	1.00	<1	20	77	39	5.39	<10	1.62	503	3	0.02	88	580	12	<5	<20	128	<0.01	<10	8	<10	<1	60
7	22577	<0.2	0.31	95	60	<5	0.74	<1	20	70	50	4.81	<10	1.01	280	4	0.02	76	510	28	<5	<20	85	<0.01	<10	8	<10	<1	71
8	22578	0.8	0.32	105	60	10	1.81	2	18	69	87	7.80	<10	1.02	435	11	0.02	75	1250	72	<5	<20	183	<0.01	<10	30	<10	<1	226
9	22579	0.4	0.28	175	45	5	0.72	<1	26	42	24	5.83	<10	1.78	663	4	0.02	115	550	20	<5	<20	86	<0.01	<10	7	<10	<1	111
10	22580	<0.2	0.26	110	40	10	1.43	<1	21	62	44	5.63	<10	1.70	795	4	0.02	91	610	16	<5	<20	150	<0.01	<10	7	<10	<1	110
11	22581	<0.2	0.25	25	50	5	0.77	1	20	60	41	5.21	<10	1.61	483	4	0.03	94	500	16	<5	<20	67	<0.01	<10	7	<10	<1	134
12	22582	0.4	0.23	45	45	5	1.26	<1	27	65	66	5.56	<10	1.68	618	4	0.03	96	500	38	<5	<20	135	<0.01	<10	7	<10	<1	137
13	22583	0.2	0.25	35	40	5	1.57	<1	21	57	45	4.82	<10	1.75	705	4	0.03	98	510	50	<5	<20	136	<0.01	<10	8	<10	<1	125
14	22584	<0.2	0.24	25	35	<5	1.67	<1	22	60	42	4.65	<10	1.65	598	3	0.03	83	460	18	<5	<20	126	<0.01	<10	7	<10	<1	128
15	22585	0.4	0.23	50	45	<5	1.43	2	26	71	50	5.52	<10	1.73	731	4	0.02	109	670	220	<5	<20	96	<0.01	<10	9	<10	<1	190
16	22586	0.2	0.47	50	50	<5	1.57	<1	23	67	61	4.71	<10	1.46	624	3	0.02	89	460	32	<5	<20	152	<0.01	<10	11	<10	<1	104
17	22587	0.2	0.74	30	35	5	1.20	1	21	59	38	5.17	<10	1.74	706	4	0.01	97	520	22	<5	<20	89	<0.01	<10	15	<10	<1	114

QC DATA:**Resplit:**

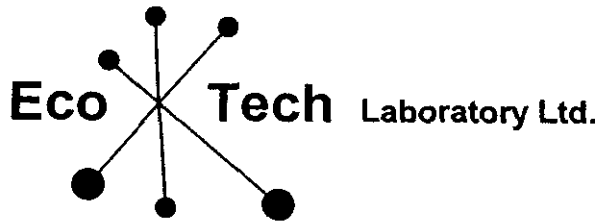
1	22571	0.2	0.17	15	45	<5	2.17	<1	18	49	31	5.57	<10	1.54	596	4	0.02	57	740	14	<5	<20	150	<0.01	<10	7	<10	<1	98
---	-------	-----	------	----	----	----	------	----	----	----	----	------	-----	------	-----	---	------	----	-----	----	----	-----	-----	-------	-----	---	-----	----	----

Repeat:

1	22571	0.3	0.19	20	45	<5	2.19	<1	17	62	29	5.52	<10	1.54	596	3	0.02	60	730	12	<5	<20	152	<0.01	<10	7	<10	<1	97
---	-------	-----	------	----	----	----	------	----	----	----	----	------	-----	------	-----	---	------	----	-----	----	----	-----	-----	-------	-----	---	-----	----	----

Standard:

GEO'05		1.5	1.41	50	135	<5	1.31	<1	16	55	83	3.56	<10	0.76	557	<1	0.02	25	560	20	<5	<20	55	0.08	<10	63	<10	9	73
--------	--	-----	------	----	-----	----	------	----	----	----	----	------	-----	------	-----	----	------	----	-----	----	----	-----	----	------	-----	----	-----	---	----



ASSAYING
GEOCHEMISTRY
ANALYTICAL CHEMISTRY
ENVIRONMENTAL TESTING

10041 Dallas Drive, Kamloops, BC V2C 6T4
Phone (250) 573-5700 Fax (250) 573-4557
E-mail: info@ecotechlab.com
www.ecotechlab.com

CERTIFICATE OF ASSAY AK 2005-013

NAVASOTA RESOURCES
#207 141 VICTORIA STREET
KAMLOOPS, BC
V2C 1Z5

17-Jan-05

No. of samples received: 9
Sample type: Core
Project #: Not Indicated
Shipment #: 05-02
Samples submitted by: R. Whiteaker

ET #.	Tag #	Au (g/t)	Au (oz/t)
1	22588	<0.03	<0.001
2	22589	<0.03	<0.001
3	22590	0.06	0.002
4	22591	0.03	0.001
5	22592	<0.03	<0.001
6	22593	<0.03	<0.001
7	22594	0.04	0.001
8	22595	0.04	0.001
9	22596	<0.03	<0.001

QC DATA:

Repeat:			
1	22588	<0.03	<0.001
Resplit:			
1	22588	<0.03	<0.001
Standard:			
SH13		1.35	0.039

JJ/jm
XLS/05

Jutta Jealous
ECO TECH LABORATORY LTD.
Jutta Jealous
B.C. Certified Assayer

ECO TECH LABORATORY LTD.
10041 Dallas Drive
KAMLOOPS, B.C.
V2C 6T4

ICP CERTIFICATE OF ANALYSIS AK 2005-013

NAVASOTA RESOURCES
#207 141 VICTORIA STREET
KAMLOOPS, BC
V2C 1Z5

Phone: 250-573-5700
Fax : 250-573-4557

No. of samples received: 9
Sample type: Core
Project #: Not Indicated
Shipment #: 05-02
Samples submitted by: R. Whiteaker

Values in ppm unless otherwise reported


Et #.	Tag #	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
1	22588	0.2	0.27	145	60	<5	0.61	<1	21	47	46	5.42	<10	1.62	492	2	0.03	118	630	14	<5	<20	83	<0.01	<10	6	<10	<1	146
2	22589	2.1	0.26	115	55	<5	0.81	<1	17	126	31	4.22	<10	1.27	425	3	0.02	93	410	366	<5	<20	129	<0.01	<10	7	<10	<1	65
3	22590	<0.2	0.26	125	40	<5	2.91	<1	18	75	49	4.85	<10	1.87	1087	2	0.02	101	1430	18	<5	<20	352	<0.01	<10	9	<10	<1	53
4	22591	<0.2	0.23	145	55	<5	1.18	<1	23	64	59	5.38	<10	1.63	580	3	0.02	120	610	20	<5	<20	133	<0.01	<10	7	<10	<1	80
5	22592	0.2	0.21	130	50	<5	1.15	<1	20	36	90	5.35	<10	1.66	497	2	0.03	111	530	20	<5	<20	126	<0.01	<10	6	<10	<1	128
6	22593	<0.2	0.21	130	50	<5	1.33	<1	26	82	25	4.43	<10	1.52	355	3	0.03	100	830	8	<5	<20	153	<0.01	<10	8	<10	<1	55
7	22594	<0.2	0.18	145	45	<5	1.67	<1	20	79	30	4.43	<10	1.52	792	2	0.02	102	530	16	<5	<20	163	<0.01	<10	5	<10	<1	49
8	22595	<0.2	0.30	140	60	<5	1.31	1	23	77	29	5.76	<10	1.90	693	2	0.02	114	540	20	<5	<20	176	<0.01	<10	9	<10	<1	75
9	22596	<0.2	0.22	20	50	<5	0.96	1	25	52	68	5.57	<10	1.67	625	3	0.04	119	660	20	<5	<20	105	<0.01	<10	7	<10	<1	111

QC DATA:Resplit:

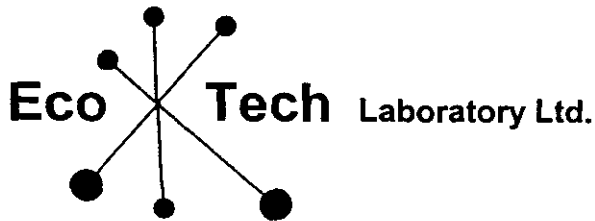
1	22588	<0.2	0.28	150	60	<5	0.62	<1	23	45	44	5.55	<10	1.62	505	3	0.03	122	670	14	<5	<20	79	<0.01	<10	7	<10	<1	138
---	-------	------	------	-----	----	----	------	----	----	----	----	------	-----	------	-----	---	------	-----	-----	----	----	-----	----	-------	-----	---	-----	----	-----

Standard:

3EO'05		1.5	1.39	45	160	<5	1.30	1	15	58	88	3.64	<10	0.75	571	<1	0.03	30	590	22	<5	<20	50	0.11	<10	68	<10	9	76
--------	--	-----	------	----	-----	----	------	---	----	----	----	------	-----	------	-----	----	------	----	-----	----	----	-----	----	------	-----	----	-----	---	----


ECO TECH LABORATORY LTD.
Jutta Jealous
BC Certified Assayer

IJ/jm
#13
CLS/05



ASSAYING
GEOCHEMISTRY
ANALYTICAL CHEMISTRY
ENVIRONMENTAL TESTING

10041 Dallas Drive, Kamloops, BC V2C 6T4
Phone (250) 573-5700 Fax (250) 573-4557
E-mail: info@ecotechlab.com
www.ecotechlab.com

CERTIFICATE OF ASSAY AK 2005-21

NAVASOTA RESOURCES
#207 141 VICTORIA STREET
KAMLOOPS, BC
V2C 1Z5

31-Jan-05

No. of samples received: 10
Sample type: Not Indicated
Project #: Not Indicated
Shipment #: 05-03
Samples submitted by: R. Whiteaker

ET #.	Tag #	Au (g/t)	Au (oz/t)
1	22501	0.04	0.001
2	22502	0.04	0.001
3	22503	0.04	0.001
4	22504	0.07	0.002
5	22505	0.05	0.001
6	22506	<0.03	<0.001
7	22597	<0.03	<0.001
8	22598	<0.03	<0.001
9	22599	<0.03	<0.001
10	22600	0.08	0.002

QC DATA:

Repeat:

1	22501	0.05	0.001
4	22504	0.07	0.002

Resplit:

1	22501	<0.03	<0.001
---	-------	-------	--------

Standard:

OXE21		0.73	0.021
-------	--	------	-------

JJ/jm
XLS/05

ECO TECH LABORATORY LTD.

Jutta Jealous
B.C. Certified Assayer

ECO TECH LABORATORY LTD.
10041 Dallas Drive
KAMLOOPS, B.C.
V2C 6T4

ICP CERTIFICATE OF ANALYSIS AK 2005-021

NAVASOTA RESOURCES
#207 141 VICTORIA STREET
KAMLOOPS, BC
V2C 1Z5

Phone: 250-573-5700
Fax : 250-573-4557

No. of samples received: 10
Sample type: Not Indicated
Project #: Not Indicated
Shipment #: 05-03
Samples submitted by: R. Whiteaker

Values in ppm unless otherwise reported

Et #.	Tag #	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Tl %	U	V	W	Y	Zn
1	22501	<0.2	0.32	140	60	5	1.14	<1	22	37	48	5.15	<10	1.64	709	4	0.02	100	680	10	<5	<20	97	<0.01	<10	6	<10	<1	91
2	22502	<0.2	0.31	110	60	<5	1.65	<1	20	47	43	5.22	<10	1.51	595	4	0.02	77	870	12	<5	<20	138	<0.01	<10	7	<10	<1	85
3	22503	0.2	0.41	185	55	5	1.94	<1	24	49	54	5.86	<10	1.30	949	5	0.02	93	440	30	<5	<20	163	<0.01	<10	6	<10	<1	58
4	22504	0.2	0.30	135	55	<5	1.74	<1	20	40	47	4.73	<10	1.39	697	3	0.02	74	410	38	<5	<20	153	<0.01	<10	6	<10	<1	130
5	22505	<0.2	0.26	70	45	<5	0.96	<1	13	101	21	3.56	<10	0.98	382	4	0.01	49	420	14	<5	<20	54	<0.01	<10	4	<10	<1	33
6	22506	0.2	0.58	130	65	5	1.20	<1	24	24	50	5.35	<10	1.47	477	4	0.02	101	810	30	<5	<20	101	<0.01	<10	6	<10	<1	99
7	22597	<0.2	0.28	130	40	<5	1.22	<1	22	76	20	5.08	<10	1.54	828	4	0.02	98	470	12	<5	<20	117	<0.01	<10	6	<10	<1	74
8	22598	<0.2	0.24	115	40	5	1.37	<1	18	77	28	4.70	<10	1.44	722	3	0.02	75	460	8	<5	<20	114	<0.01	<10	6	<10	<1	56
9	22599	<0.2	0.24	160	50	5	1.06	<1	22	87	23	4.85	<10	1.33	530	5	0.01	94	510	20	<5	<20	98	<0.01	<10	5	<10	<1	141
10	22600	<0.2	0.37	150	65	<5	1.05	<1	25	42	72	5.77	<10	1.70	668	4	0.02	113	690	12	<5	<20	103	<0.01	<10	7	<10	<1	98

QC DATA:**Repeat:**

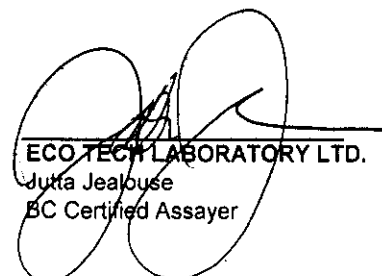
1	22501	<0.2	0.33	145	60	<5	1.16	<1	23	38	49	5.22	<10	1.64	715	4	0.02	100	700	12	<5	<20	95	<0.01	<10	6	<10	<1	103
---	-------	------	------	-----	----	----	------	----	----	----	----	------	-----	------	-----	---	------	-----	-----	----	----	-----	----	-------	-----	---	-----	----	-----

Resplit:

1	22501	<0.2	0.31	145	55	<5	1.15	<1	24	37	46	5.20	<10	1.63	709	4	0.02	98	680	12	<5	<20	96	<0.01	<10	6	<10	<1	108
---	-------	------	------	-----	----	----	------	----	----	----	----	------	-----	------	-----	---	------	----	-----	----	----	-----	----	-------	-----	---	-----	----	-----

Standard:

GEO'05		1.5	1.39	55	140	<5	1.27	<1	15	50	85	3.38	<10	0.82	546	<1	0.02	28	590	22	<5	<20	51	0.11	<10	62	<10	9	73
--------	--	-----	------	----	-----	----	------	----	----	----	----	------	-----	------	-----	----	------	----	-----	----	----	-----	----	------	-----	----	-----	---	----


ECO TECH LABORATORY LTD.
Jutta Jealous
BC Certified Assayer

ECO TECH LABORATORY LTD.
10041 Dallas Drive
KAMLOOPS, B.C.
V2C 6T4

ICP CERTIFICATE OF ANALYSIS AK 2005-056

NAVASOTA RESOURCES
#207 141 VICTORIA STREET
KAMLOOPS, BC
V2C 1Z5

Phone: 250-573-5700
Fax : 250-573-4557

*GOLD CREEK
INV # AK 05-56
02/25/05*

No. of samples received: 17
Sample type: Core
Project #: Gold Ck
Shipment #: Not indicated
Samples submitted by: Royanna Wild

Values in ppm unless otherwise reported

Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
1	22507	20	0.7	0.12	25	105	<5	1.67	<1	3	135	34	1.62	<10	0.83	289	8	0.01	33	120	18	<5	<20	280	<0.01	<10	19	<10	<1	88
2	22508	25	0.7	0.18	30	90	<5	0.45	<1	4	118	44	1.68	<10	0.27	148	9	0.01	39	80	12	<5	<20	84	<0.01	<10	18	<10	<1	102
3	22509	25	0.3	0.16	30	115	<5	2.42	2	4	110	16	1.94	<10	1.09	547	11	0.01	31	520	12	5	<20	455	<0.01	<10	56	<10	3	146
4	22510	35	0.2	0.11	45	100	<5	0.46	<1	9	103	38	1.79	<10	0.28	703	3	<0.01	23	120	6	<5	<20	58	<0.01	<10	3	<10	<1	40
5	22511	15	<0.2	0.14	40	100	<5	0.52	<1	7	116	27	1.51	<10	0.28	415	2	<0.01	20	120	10	<5	<20	69	<0.01	<10	3	<10	<1	32
6	22512	10	<0.2	<0.01	<5	<5	<5	0.09	<1	<1	181	2	0.27	<10	0.04	40	4	<0.01	3	40	<2	<5	<20	14	<0.01	<10	<1	<10	<1	1
7	22513	60	0.7	0.37	50	90	<5	0.78	3	7	98	42	2.24	<10	0.49	219	10	<0.01	53	660	28	<5	<20	173	<0.01	<10	13	<10	2	285
8	22514	40	<0.2	0.49	50	140	<5	0.57	2	13	46	30	3.36	<10	0.68	343	5	0.01	34	550	10	<5	<20	96	<0.01	<10	5	<10	<1	226
9	22515	20	<0.2	0.40	45	175	<5	0.55	1	13	47	35	3.29	<10	0.65	345	5	0.01	37	590	10	<5	<20	88	<0.01	<10	7	<10	<1	269
10	22516	25	<0.2	0.29	70	245	<5	0.29	<1	9	86	13	3.61	20	0.80	281	4	0.02	77	570	14	<5	<20	42	<0.01	<10	4	<10	<1	79
11	22517	645	0.5	0.09	20	125	<5	0.57	<1	1	164	10	0.75	<10	0.25	101	1	<0.01	16	90	10	<5	<20	98	<0.01	<10	5	<10	<1	14
12	22518	960	0.5	0.15	155	65	<5	0.89	<1	11	89	38	3.24	<10	0.67	194	6	<0.01	65	280	52	<5	<20	159	<0.01	<10	10	<10	<1	114
13	22519	15	1.9	0.14	25	265	<5	0.34	<1	2	98	679	1.48	<10	0.59	86	2	<0.01	18	320	12	<5	<20	143	<0.01	<10	7	<10	<1	89
14	22520	30	<0.2	0.15	35	320	<5	0.11	<1	3	74	39	1.81	<10	0.65	51	2	<0.01	21	450	4	<5	<20	42	<0.01	<10	5	<10	<1	58
15	22521	30	0.3	0.21	55	160	<5	0.67	<1	6	79	30	2.13	<10	0.59	130	2	<0.01	32	820	58	<5	<20	222	<0.01	<10	6	<10	1	40
16	22522	5	<0.2	0.15	35	330	<5	0.38	<1	4	75	37	1.61	<10	0.61	87	2	<0.01	28	380	4	<5	<20	58	<0.01	<10	5	<10	<1	49
17	22523	25	<0.2	0.14	45	325	<5	0.42	<1	4	72	37	1.55	<10	0.64	104	1	<0.01	31	260	4	<5	<20	55	<0.01	<10	5	<10	<1	42

QC DATA:

Repeat:

1	22507	30	0.5	0.12	20	110	<5	1.64	<1	3	133	32	1.59	<10	0.81	288	8	<0.01	31	120	16	5	<20	270	<0.01	<10	19	<10	<1	86
11	22517	640	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-
12	22518	990	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-

Resplit:

1	22507	35	0.5	0.11	25	100	<5	1.64	<1	4	118	31	1.60	<10	0.80	284	8	<0.01	31	120	24	5	<20	264	<0.01	<10	19	<10	<1	90
---	-------	----	-----	------	----	-----	----	------	----	---	-----	----	------	-----	------	-----	---	-------	----	-----	----	---	-----	-----	-------	-----	----	-----	----	----

Standard:

GEO'05	-	1.5	1.49	55	145	5	1.38	<1	16	58	84	3.79	<10	0.80	591	1	0.03	25	620	20	<5	<20	59	0.11	<10	61	<10	10	72	
OXE21	630	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-

Jutta Jealous
ECO TECH LABORATORY LTD.
Jutta Jealous
BC Certified Assayer

ECO TECH LABORATORY LTD.
10041 Dallas Drive
KAMLOOPS, B.C.
V2C 6T4

ICP CERTIFICATE OF ANALYSIS AK 2005-72

NAVASOTA RESOURCES
#207 141 VICTORIA STREET
KAMLOOPS, BC
V2C 1Z5

Phone: 250-573-5700
Fax : 250-573-4557

No. of samples received: 11
Sample type: Rock
Project #: Gold CK
Shipment #: Not Indicated
Samples submitted by: Royanna Wild

Values in ppm unless otherwise reported

Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
1	22524	80	2.1	0.13	60	95	<5	0.56	<1	16	85	76	2.65	<10	0.71	147	3	<0.01	59	230	378	<5	<20	65	<0.01	<10	6	<10	<1	211
2	22525	5	0.4	0.13	45	280	<5	0.45	<1	7	83	76	1.52	<10	0.73	123	1	<0.01	34	340	6	<5	<20	51	<0.01	<10	7	<10	2	96
3	22526	5	0.2	0.62	<5	225	<5	0.47	<1	8	78	27	2.40	<10	1.07	323	2	0.01	43	520	10	<5	<20	33	<0.01	<10	17	<10	<1	92
4	22527	5	0.6	0.97	10	220	<5	1.13	<1	13	92	185	2.51	<10	1.52	327	3	0.01	55	550	18	<5	<20	68	<0.01	<10	25	<10	2	49
5	22528	5	0.2	0.13	25	380	<5	0.30	<1	3	73	15	1.67	<10	0.65	82	2	<0.01	26	270	6	<5	<20	49	<0.01	<10	5	<10	<1	38
6	22529	15	0.2	1.76	5	25	10	0.51	<1	27	31	23	2.66	<10	1.93	305	1	0.02	44	200	22	<5	<20	17	0.10	<10	13	<10	3	25
7	22530	10	0.2	2.64	<5	35	15	0.65	<1	45	17	17	5.87	<10	2.24	554	2	0.02	58	200	32	<5	<20	22	0.23	<10	179	<10	<1	48
8	22531	10	<0.2	2.37	<5	40	5	0.87	<1	43	31	182	5.82	<10	1.88	562	3	0.02	23	280	28	<5	<20	23	0.19	<10	204	<10	2	53
9	22532	10	0.4	3.14	5	50	<5	8.20	<1	36	14	233	7.14	<10	2.20	1105	4	0.03	14	280	28	<5	<20	210	0.06	<10	455	<10	5	54
10	22533	5	<0.2	1.81	<5	25	10	0.67	<1	30	44	25	4.69	<10	1.22	433	2	0.04	5	700	24	<5	<20	21	0.15	<10	63	<10	11	48
11	22534	10	0.2	2.40	10	35	<5	2.44	<1	44	52	149	5.87	<10	1.87	593	2	0.01	23	270	26	<5	<20	46	0.23	<10	198	<10	<1	54

QC DATA:**Resplit:**

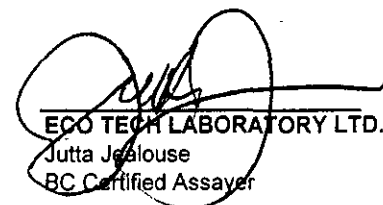
1	22524	85	1.8	0.12	65	95	<5	0.58	1	16	100	80	2.56	<10	0.70	149	3	<0.01	59	230	450	<5	<20	65	<0.01	<10	6	<10	<1	220
---	-------	----	-----	------	----	----	----	------	---	----	-----	----	------	-----	------	-----	---	-------	----	-----	-----	----	-----	----	-------	-----	---	-----	----	-----

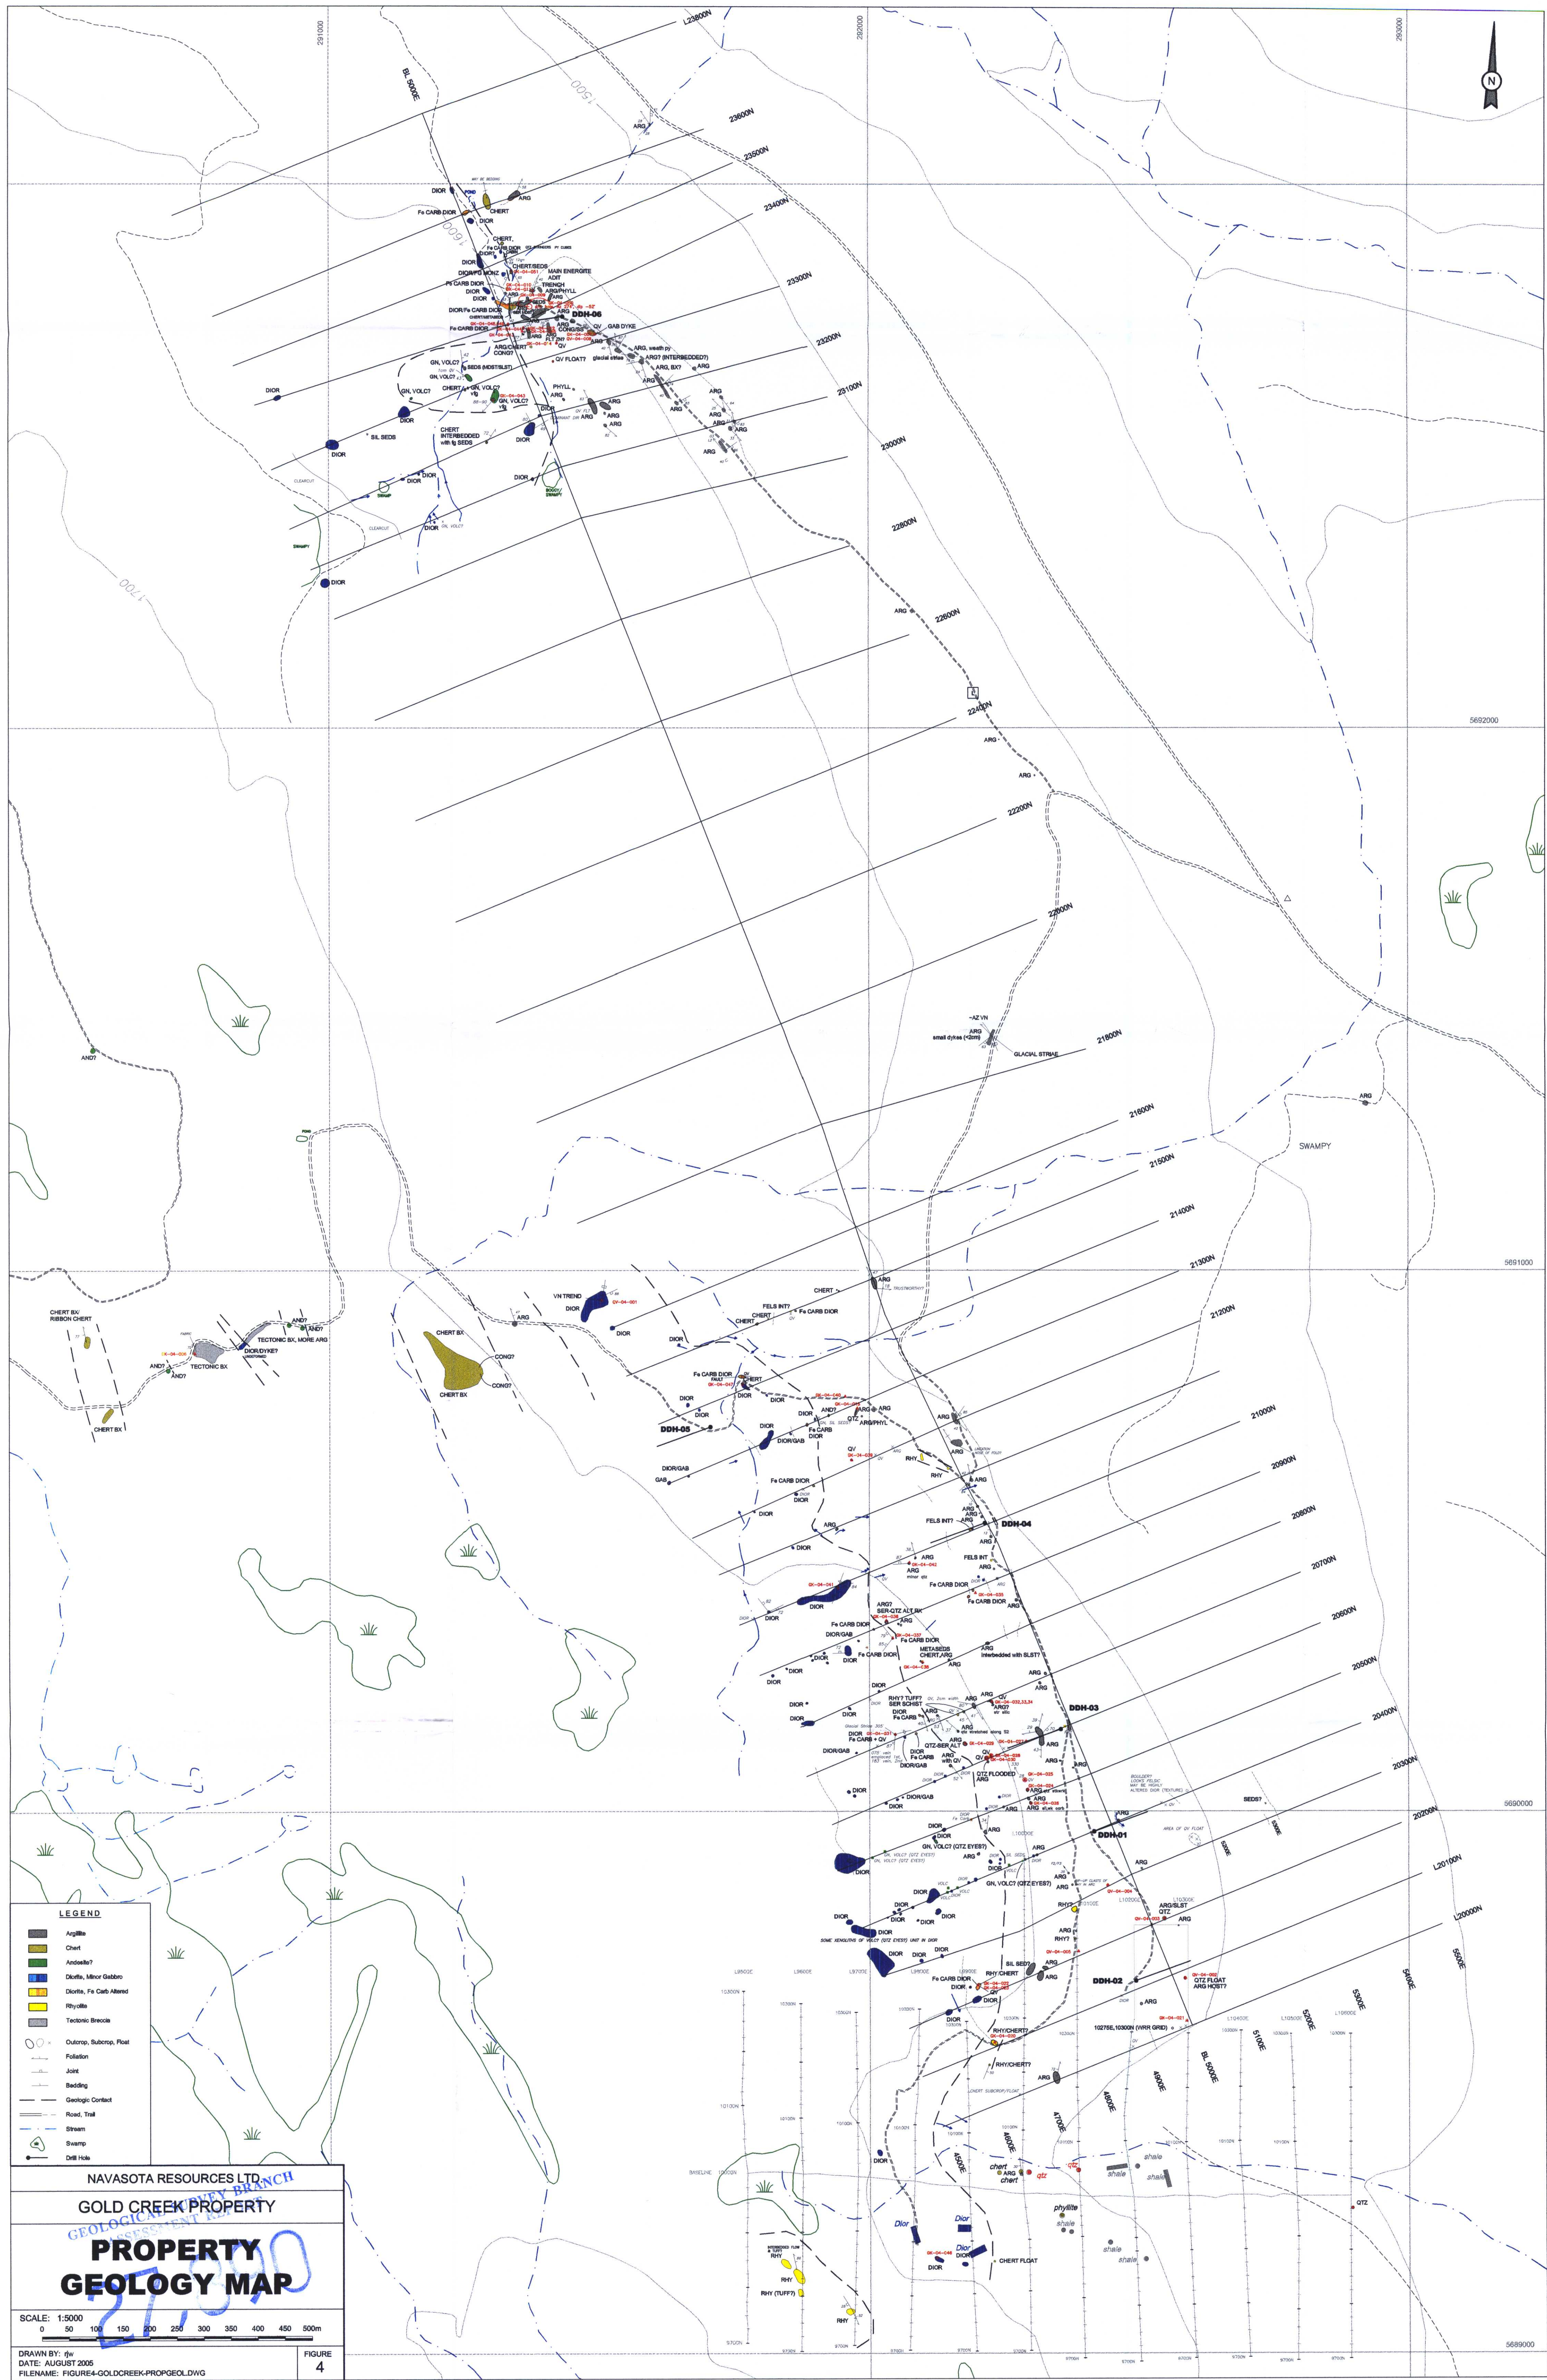
Repeat:

1	22524	85	1.9	0.13	65	80	<5	0.58	<1	17	86	76	2.68	<10	0.73	149	2	<0.01	60	240	374	<5	<20	66	<0.01	<10	6	<10	<1	223
---	-------	----	-----	------	----	----	----	------	----	----	----	----	------	-----	------	-----	---	-------	----	-----	-----	----	-----	----	-------	-----	---	-----	----	-----

Standard:

GEO'05		135	1.6	1.39	55	140	<5	1.32	<1	16	54	85	3.51	<10	0.77	573	<1	0.02	28	610	22	<5	<20	55	0.08	<10	62	<10	9	73
--------	--	-----	-----	------	----	-----	----	------	----	----	----	----	------	-----	------	-----	----	------	----	-----	----	----	-----	----	------	-----	----	-----	---	----


ECO TECH LABORATORY LTD.
Jutta Jalouse
BC Certified Assayer



LEGEND

[Symbol]	Argills
[Symbol]	Chert
[Symbol]	Andesite?
[Symbol]	Diorite, Minor Gabbro
[Symbol]	Diorite, Fe Carb Altered
[Symbol]	Rhyolite
[Symbol]	Tectonic Breccia
[Symbol]	Outcrop, Subcrop, Plot
[Symbol]	Fault
[Symbol]	Joint
[Symbol]	Bedding
[Symbol]	Geologic Contact
[Symbol]	Road, Trail
[Symbol]	Stream
[Symbol]	Swamp
[Symbol]	Dike Hole

NAVASOTA RESOURCES LTD.
 GOLD CREEK PROPERTY
**PROPERTY
 GEOLOGY MAP**

SCALE: 1:5000
 0 50 100 150 200 250 300 350 400 450 500m

DRAWN BY: rfv
 DATE: AUGUST 2005
 FILENAME: FIGURE4-GOLDCREEK-PROPGEOL.DWG

FIGURE
4



LEGEND

25 Au, ppb: 2005 Soil Sample
 10 Au, ppb: pre-2005 Soil Sample

Drainage
 Grid Line
 Road
 Swamp

NAVASOTA RESOURCES LTD.
 GOLD CREEK PROPERTY

**Au-in-Soils
 Geochemistry**

SCALE: 1:5000
 0 50 100 150 200 250 300 350 400 450 500m

DRAWN BY: RW
 DATE: AUGUST 2005
 FILENAME: FIGURES-GOLDCREEK-GEOCHEM-AU.DWG

FIGURE
 5

NAVASOTA SURVEY BRANCH
 GOLD CREEK PROPERTY