

2005 SOIL GEOCHEMISTRY REPORT

on the

Barnes Creek Property

**Lat. 49° 58' North
Long. 117° 47' West
Trim Map #: 082L.009, 082L.019
NTS: 82L/1**

For

**COLUMBIA YUKON EXPLORATIONS INC.
2489 Bellevue Ave
West Vancouver, BC
V7V 1E1**

**By: Bernhardt Augsten, P.Geo.
November, 2005**

TABLE OF CONTENTS

1.0	SUMMARY.....	1
2.0	INTRODUCTION.....	2
3.0	LOCATION, ACCESS AND PHYSIOGRAPHY	2
4.0	CLAIM STATUS.....	4
5.0	REGIONAL AND LOCAL GEOLGY	6
6.0	EXPLORATION HISTORY	7
7.0	SOIL GEOCHEMISTRY	9
7.1	<u>METHODOLOGY</u>	9
7.2	<u>ANALYTICAL METHODS</u>	11
7.3	<u>RESULTS</u>	11
8.0	CONCLUSIONS AND RECOMMENDATIONS	14
9.0	COST STATEMENT	15
10.0	REFERENCES	16
11.0	CERTIFICATE OF AUTHOR	18

LIST OF TABLES

Table 1	CLAIM DATA.....	4
Table 2:	ANALYTICAL STATISTICS	12

LIST OF FIGURES

Figure 1:	LOCATION MAP	3
Figure 2:	CLAIM MAP	5
Figure 3:	SOIL GRID LOCATION MAP	10
Figure 4:	HOLMES LAKE GRID – GOLD SOIL GEOCHEMISTRY (IN POCKET)	
Figure 5:	HOLMES LAKE GRID – SILVER SOIL GEOCHEMISTRY (IN POCKET)	
Figure 6:	HOLMES LAKE GRID – ARSENIC SOIL GEOCHEMISTRY (IN POCKET)	

LIST OF APPENDICES

APPENDIX I SOIL ANALYSES

1.0 SUMMARY

This report summarizes the results of a soil geochemistry program that was conducted on the Barnes Creek Property in the 2005 field season. The soil program was focused on Tenure #504861 (formerly Barnes 7) and was a continuation of a small soil program carried out in the latter part of 2004 on the Holmes Lake Grid. In 2004, 185 soils were collected on six lines which produced significant gold-silver-arsenic anomalies, notably a northerly-trending linear anomaly extending for 500 metres and open to the north, south and east. In 2005, a further 794 soils were collected on an expanded Holmes Lake Grid. In March 2005, part of the original soil anomaly was trenched.

The Holmes Lake Grid now covers an area of approximately 1.7 kilometres by 1.3 kilometres. The completed soil coverage has identified several significant gold and arsenic soil anomalies. The most important of these is a broad northwest-trending anomaly approximately 1200 metres by 300 metres in size, and open both to the northwest and southeast. This anomaly is located on the northern part of the grid. The vein discoveries made earlier this year occurred at the southeast end of this anomaly and corresponded to high gold in soil values of 1280ppb with accompanying high silver and arsenic. Further to the northwest, gold in soils attained maximum values of 350ppb, and arsenic in soils attained maximum values of 875ppm. There is generally an excellent correlation between gold and arsenic. Although outcrop exposure in the area of this anomaly is limited, that which is seen is dominated by a feldspar porphyry or feldspar porphyritic diorite.

On the southern part of the soil grid there is another northwest-trending anomaly parallel to the northern anomaly although more poorly defined. It is best described as a series of anomalous clusters of gold and arsenic soil anomalies which together define the northwest trend. Within this southern anomaly high values of 365ppb gold and 300ppm arsenic were obtained. Interestingly, visible gold was panned from the 365ppb gold anomaly.

An extensive trenching program is proposed to test all significant gold anomalies.

2.0 INTRODUCTION

This report details the result of a soil geochemistry program which was conducted on the Barnes Creek Property (the property), located west of Lumby, British Columbia. The program was carried out by Columbia Yukon Explorations Inc. in the summer of 2005.

A total of 794 B-horizon soil samples were collected and analyzed for gold and 28 other elements. This program was an extension of a small program of soil sampling started in the fall of 2005 on the ‘Holmes Lake’ grid. The original program resulted in significant gold, arsenic, and silver anomalies which were trenched in March 2005, and reported on separately.

3.0 LOCATION, ACCESS AND PHYSIOGRAPHY

The Barnes Creek Project is located in the Whatshan Range of the Monashee Mountains of southern British Columbia. The project area is 70 kilometers east-southeast of Vernon, and 27 kilometers northwest of the Needles ferry on Arrow Lake (see Figure 1).

Access into the claim blocks is excellent due to an array of well-maintained logging roads operated by Pope and Talbot to the east of the divide, and Tolko Industries to the west of the divide. The south and eastern parts of the property are accessed via the Whatshan Lake Settlement Road, which starts three kilometres west of the Needles Ferry off Highway 6. The property is 32 kilometres up this road. The west and northern parts of the property are accessed via the Keefer Lake FSR, which leaves Provincial Highway 6 32 kilometres east of the Needles Ferry. The property is 24 kilometres up this road. Although four-wheel drive is recommended, the majority of the roads are accessible with two-wheel drive.

The local physiography consists of mountainous terrain with somewhat subdued topography with maximum elevations of 5900 feet, and maximum relief of approximately 1400 feet. The topography would not be considered rugged within the claim area. Four main drainages serve to delineate the general area, these being Barnes Creek to the east,

Holding Creek to the south and east, Kettle River and headwaters thereof to the north, and the east fork of Trapp Creek to the south and west.



Figure 1: LOCATION MAP

4.0 CLAIM STATUS

The Barnes Creek project currently consists of 26 contiguous claims; KBM 1 – 14, and Barnes 1 – 12 (see Figure 2). Table 1 below lists the pertinent claim data.

Table 1 CLAIM DATA

CLAIM NAME	TENURE #	# Hectares	EXPIRY DATE*
KBM 1	394004	25	June 2, 2011
KBM 2	394005	25	June 2, 2011
KBM 3	394006	25	June 2, 2011
KBM 4	394007	25	June 2, 2011
KBM 5	394008	25	June 2, 2011
KBM 6	394009	25	June 2, 2011
KBM 7	394010	25	June 2, 2011
KBM 8	394011	25	June 2, 2011
KBM 9	394012	25	June 2, 2011
KBM 10	394013	25	June 2, 2011
KBM 11	394014	25	June 2, 2011
KBM 12	394015	25	June 2, 2011
KBM 13	394016	25	June 2, 2011
KBM 14	394017	25	June 2, 2011
BARNES 1	403336	300	June 2, 2012
BARNES 2	403337	500	June 2, 2012
BARNES 3	403338	225	June 2, 2012
BARNES 4	403339	500	June 2, 2012
BARNES 5	405691	375	June 2, 2012
BARNES 6	405692	300	June 2, 2012
BARNES 7 ¹	504861	746	June 2, 2012
BARNES 8 ¹	505209	498	June 2, 2012
BARNES 9 ¹	505208	684	June 2, 2012
BARNES 10	407896	475	June 2, 2011
BARNES 11	502349	393	January 12, 2006
BARNES 12	504447	166	January 21, 2006

¹ Claims converted to new claim system; therefore, new tenure numbers.

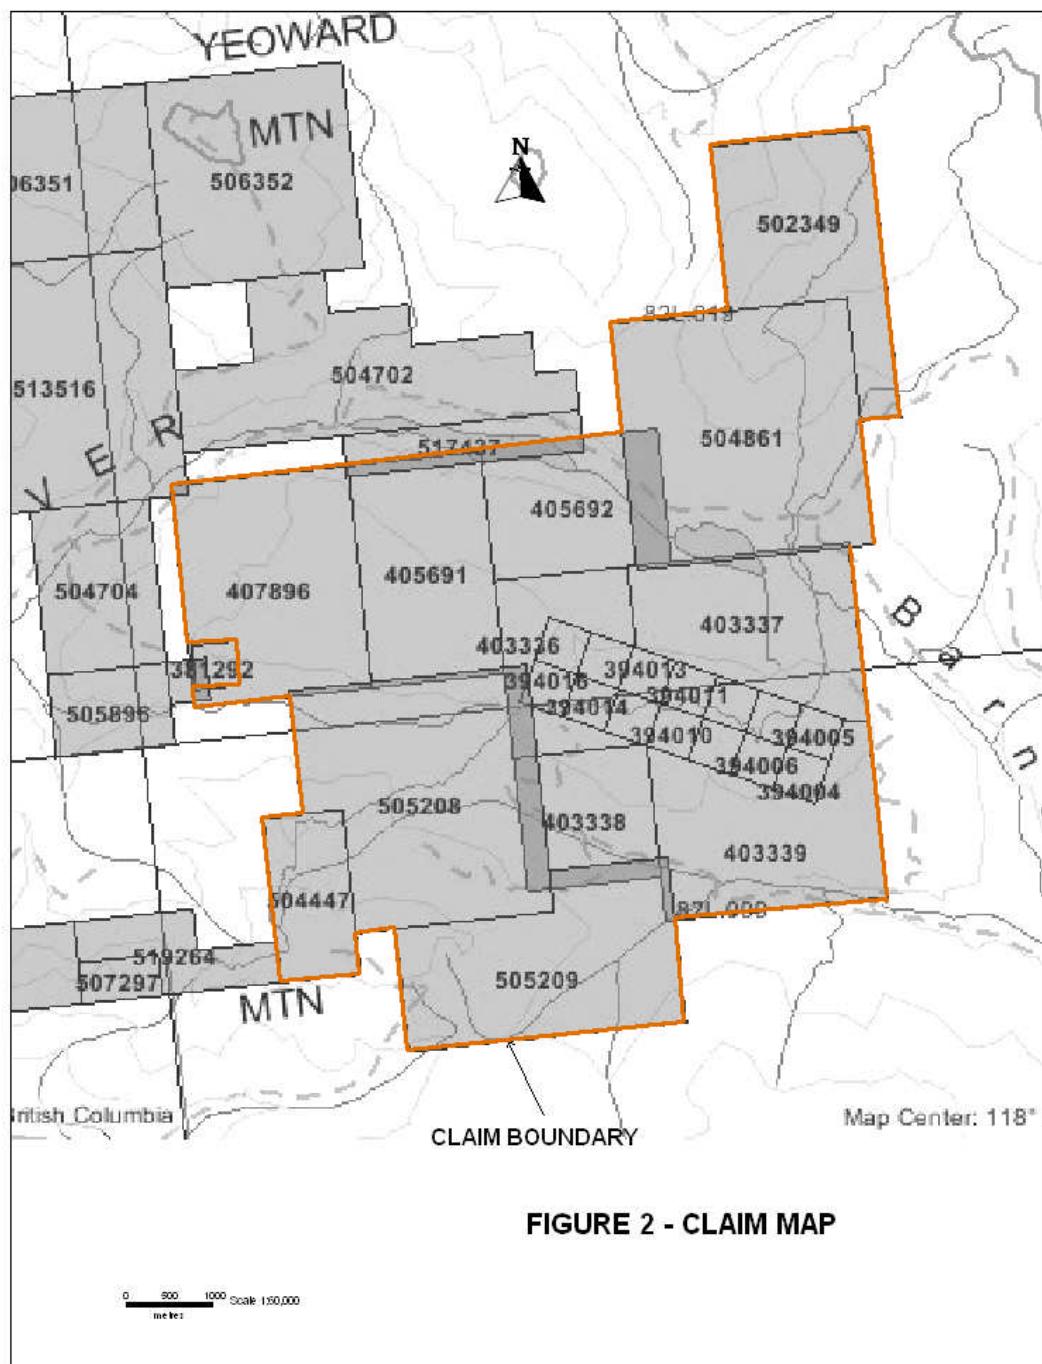


Figure 2: CLAIM MAP

5.0 REGIONAL AND LOCAL GEOLGY

The regional geology in the vicinity of the Barnes Creek Project has not been adequately described in past work by either Provincial or Federal agencies and various interpretations exist. GSC Open File #637 shows the area as being underlain by Paleozoic-aged volcanic and sedimentary assemblage consisting of pelite, quartzite, conglomerate, argillaceous and graphitic limestone, black shale, andesite and tuff - all considered to be part of the Thompson Assemblage (Okulitch, 1979). A more recent compilation shows the entire claim block underlain by rocks of the Harper Ranch Group which include hemipelagic tuffaceous mudstone, chert, limestone, and arc derived sandstone and conglomerate (Hoy et al, 1994). The Harper Ranch Group is considered to be the basement to Quesnellia. The most current work in the area is a recent publication by the GSC which is in part a compilation of past work and some new mapping (Thompson et al, 2003). This map shows that the majority of the Barnes Creek Property is underlain by Upper Triassic Slocan Group siliciclastic rocks comprised of grey to black phyllite, quartzite, and minor tuffaceous rocks. The map also shows a small occurrence of Upper Triassic Nicola Group volcanic rocks forming a ridge on the Barnes 7 claim. An easterly trending intrusive contact is mapped in the southeast where the Spruce Grove Batholith, a Jurassic-aged granodiorite contacts sediments of the Slocan Group. A significant northerly trending, west-dipping normal fault, ‘Bevan Fault’ transects the eastern edge of the property.

No property scale mapping has occurred to date; however, examination of some of the limited outcrop has shown that the area underlain by the claims consists of argillites, dirty limestones, polyolithic conglomerate, and a distinctive coarse-grained porphyritic diorite. The conglomerate contains predominantly lithic sedimentary clasts including argillite, chert, and limestone including some block-sized limestone clasts with a limy matrix. The porphyritic diorite occurs sporadically in outcrop along roadcuts on the Barnes 4 claim. The granodiorite, as mapped by Thompson, was seen in outcrop on the Barnes 8 claim. Significant skarning and contact effects occur in the adjacent sediments. Feldspar porphyritic flows and subvolcanic intrusions and volcaniclastic sediments were observed, but not mapped on the Barnes 7 claim. Detailed mapping is required to more fully

understand the geological relationships on the claims; however, this will be hampered by the general lack of outcrop. The existing outcrop is typically seen either at the crest of hills on roadcuts or in creek banks.

6.0 EXPLORATION HISTORY

Only limited exploration has ever occurred on or in the vicinity of the Barnes Creek Project. Previous exploration work has concentrated on the placer gold occurrences in Holding, Eureka, Barnes, and Kettle Creek. There is also some recorded placer activity in Wauchope Creek to the southwest.

Barnes Creek has a recorded placer production of 2581 grams between the years of 1935 to 1945 (Minfile #082LSE053); however, there appears to be some confusion between this placer and that of nearby Holding Creek (Minfile #082LSE045) which is probably where this production is actually from. Evidence of the historic placer workings on Holding Creek is clear. Eureka Creek had a recorded placer production of 870 grams between the years of 1931 to 1945.

The original Eureka workings date back to the late 1890's and very early 1900's. These workings consisted of two adits. In the lower adit, there was reportedly a mineralized dike containing pyrite, and averaging about two grams per tonne gold, (EMPR AR 1901).

In 1983, Golden Porphyrite Ltd. conducted a limited geochemical and prospecting survey on their Zag 1 and Zag 2 claims - parts of which occur on the Barnes 4 claim. Three significant gold values were obtained from pan concentrates in small tributaries to Eureka Creek. These were two samples greater than 10,000ppb Au, and one at 370ppb Au. Additionally, two low but highly anomalous silver values (11.5ppm and 38.0ppm) in quartz veining hosted by porphyritic diorite were obtained. Follow-up work was recommended, but never completed (Ass. Rpt. #12,338).

In 1982 and 1983, Cominco Ltd. carried out an extensive regional geochemical program consisting of regional stream sediment sampling including both silt and heavy mineral (1982), and after staking target areas, grid and contour soil sampling took place (AR#11,817).

In 1983, Beaty Geological Ltd. conducted geochemical silt sampling, rock sampling, and prospecting on ground now part of the Barnes Creek Project. Near the height of land two silt samples were collected on separate creeks - both strongly anomalous in gold. These creeks drain areas covered by the KBM 2, KBM 4, and KBM 6 claims, and the Barnes 4 claim. A detailed soil sampling program was recommended but never initiated.

In 2003, Columbia Yukon Explorations Ltd. conducted a soil geochemistry program and trenching program essentially covering the entire KBM 1-14 claim group. Significant gold arsenic anomalies were discovered. Subsequent trenching of these anomalies resulted in the discovery of narrow, very high grade, gold-bearing quartz veinlets hosted within a structurally disturbed argillaceous siltstone (Augsten, 2004). In 2004, Columbia Yukon Explorations Ltd. expanded the soil geochemistry program started in 2003 on the Barnes Main Grid, and also established a small soil grid in the south part of the property (the Eureka Grid) as well as a small grid north of Holmes Lake called the Holmes Lake Grid. Additional trenching was conducted on the Barnes Main Grid where several very small gold bearing quartz veins were discovered. The Holmes Lake soil grid outlined a strong northerly trending gold-arsenic-silver anomaly, (Augsten, 2005).


Anomalies defined in the Holmes Lake grid were trenched in March 2005, and resulted in the discovery of high grade gold and silver-bearing quartz veins hosted by feldspar porphyries, and broader zones of quartz-carbonate-pyrite altered feldspar porphyry with anomalous gold, arsenic and antimony (Augsten, 2005).

7.0 SOIL GEOCHEMISTRY

7.1 METHODOLOGY

Most soils were collected along a regular grid with line spacing of 100 metres and station spacing of 25 metres. Thirty-six soils were also collected along the main access road just north of Holmes Lake near the southern edge of the grid (see Figure 3). Two north-trending baselines were established on the Holmes Grid - one baseline at 6400E and the second at 7400E. Baselines were cut out and slope corrected with stations every 50 metres. Crosslines were established every 100 metres using a hipchain and compass with stations every 25 metres. It should also be noted that the soil grid was located and labeled to correspond to NAD83 UTM coordinates. For example, baseline 6400E corresponds to 406400E on the UTM grid, and Line 3500N (35N) corresponds to 5553500N on the UTM grid. Therefore, a station at L28N/6700E corresponds to UTM coordinate 5552800N and 406700E. Soil samples were collected on these lines every 25 metres. Every effort was made to collect the 'B' horizon soil, which usually occurred at a depth of 10 to 20 centimetres. Overburden depth appears to be less than one metre with some exceptions. Heavy overburden in the form of till occurs peripheral to a creek which flows southward from the northeastern part of the claim block around baseline 7400E particularly north of 5553000N. Samples were collected in a kraft paper envelope. A total of 794 samples were collected in the 2005 field season.

Figure 3: SOIL GRID LOCATION MAP

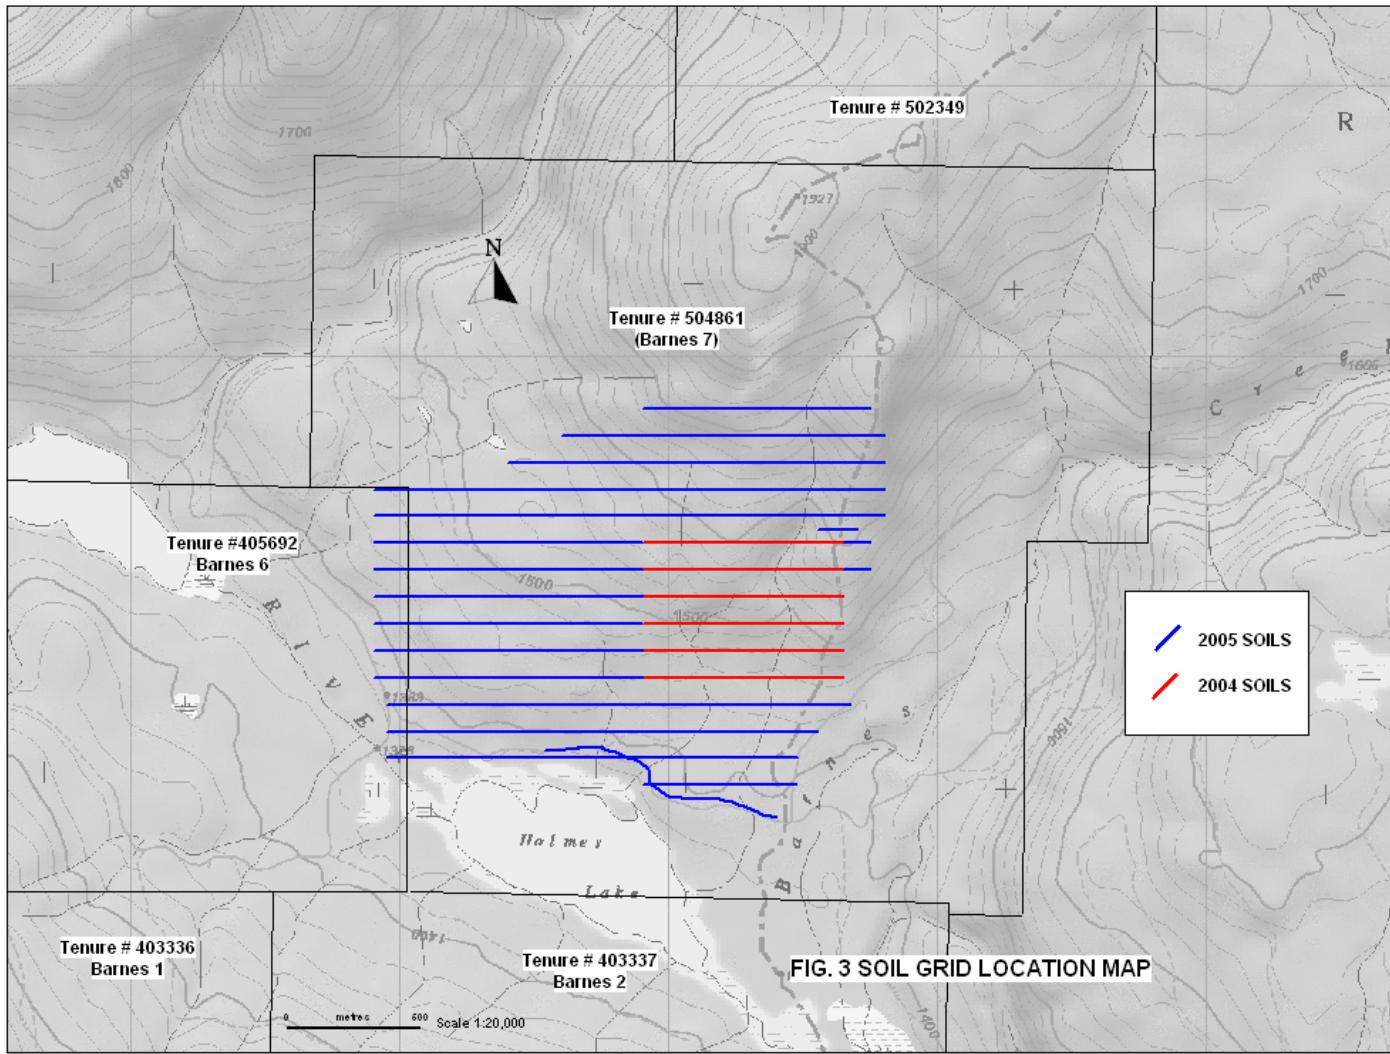

7.2 ANALYTICAL METHODS

All analytical work was conducted by EcoTech Laboratory Ltd. of Kamloops, BC. Samples are catalogued and dried. Soils are prepared by sieving through an 80 mesh screen to obtain a minus 80 mesh fraction. Samples unable to produce adequate minus 80 mesh material are screened at a coarser fraction. These samples are flagged with the relevant mesh.

Geochemical Gold Analysis:

The sample is weighed to 30 grams and fused along with proper fluxing materials. The bead is digested in aqua regia and analyzed on an atomic absorption instrument. Appropriate reference materials accompany the samples through the process allowing for quality control assessment. Results are entered and printed along with quality control data (repeats and standards).

Multielement ICP Analysis:

A 0.5 gram sample is digested with 3ml of a 3:1:2 (HCl:HN03:H20) for 90 minutes in a water bath at 95°C. The sample is then diluted to 10ml with water. The sample is analyzed on a Jarrell Ash ICP unit. Results are collated by computer and are printed along with accompanying quality control data (repeats and standards).

7.3 RESULTS

The soil program on the Holmes Lake Grid was initiated on the basis of known gold in heavy mineral concentrates from a small creek draining the ridge of the grid area, and a significant multielement RGS anomaly from the same creek. The 2005 soil program consisted of collecting a total of 794 B-horizon soils as described earlier. Analytical results for the Holmes Lake soils are listed in Appendix I. Soil results for gold, silver, and arsenic are contoured and plotted on Figure 4, Figure 5, and Figure 6 respectively, and include the complete Holmes Lake Grid data set (i.e., 2004 and 2005 soils).

ARSENIC:

Arsenic duplicates the northwest-trending gold anomaly and in fact forms a more cohesive anomaly over the 1200 metre trend (see Figure 6). Once again the anomaly remains open to the northwest and southeast and again the anomaly appears to be strongly bounded to the north and south. The overall excellent correlation with gold validates the target. Arsenic in soils is especially coherent between 7000E and 7400E between L3400N and 3500N with high values to 875ppm.

As with gold, arsenic forms a weaker northwest-trending feature at the southern part of the grid with some spotty highs, notably 300ppm As at L2500N/6900E.

SILVER:

Silver in soils shows a somewhat different pattern than that of gold and arsenic (see Figure 5). The northwest trend, so well defined by gold and arsenic, breaks down to a certain degree; although, a weak trend is still apparent defined more by small clusters of anomalous values.

A significant linear anomaly occurs between L3100N and 3200N at 7600E to 7625E with a survey high value of 8.9ppm.

As with gold and arsenic, silver also forms a west-trending feature at the southern part of the grid with particularly good consistency between 6900E and 7175E on L2500N.

Silver breaks with the patterns established for gold and arsenic in the northeast corner of the grid where a northwest trending anomaly occurs between L3400N and L3800N with very consistent anomalous values between L3400N and 3500N and 7600E to 7800E.

There appears to be a geological change at L3400N from feldspar porphyritic intrusives to argillaceous sediments. This is based more on very limited outcrop and rock chips observed in talus and soil pits. This geological change, if correct, may explain the anomalous silver values; however, not enough information is available yet to make a more accurate assessment.

8.0 CONCLUSIONS AND RECOMMENDATIONS

The 2005 soil geochemistry program on the Holmes Lake grid was successful in expanding the anomalous zones discovered late in 2004. The combination of anomalous gold, arsenic, and/or silver provides a high degree of confidence that underlying bedrock mineralization occurs as evident from trenching conducted in March, 2005.

To that end all multi-element anomalies should be trenched if physically possible.

Specific areas are as follows:

1. L3350N from 7575E to 7625E
2. L3400N from 6850E to 7275E
3. L3500N from 6710E to 6775E
4. L3500N from 7235E to 7265E
5. L3600N from 6550E to 6600E
6. L3600N from 6710E to 6735E
7. L3600N from 6785E to 6835E
8. L3700N from 6625E to 6675E
9. L2600N from 6035E to 6135E
10. L2600N from 7325E to 7365E
11. L2600N from 7510E to 7535E
12. L2500N from 6885E to 6925E
13. L2400N from 7210E to 7235E
14. Anomalous values along road in extreme southeast part of grid

In addition to the trenching, the soil geochemistry should be expanded to the northwest beyond L3700N. L3700N and L3800N should be sampled to 6400E from their present location. Also, the grid should be extended to the southeast beyond L3100N. Lines 2800N to 3100N should be extended a further 100 metres to the east. It should be noted a logging road with a wide right of way exists in this area which would affect quality of soils for at least one station. Therefore, the lines should be extended to the road initially.

9.0 COST STATEMENT

Labour	B. Augsten (June 2,3, 6-10, 13-17, 21, 13 days @\$450.00)	\$5,850.00
	K. Murray (June 6-10, 20-24, 27-30, July1, 6-9, Aug 2-4, 22 days @\$250.00)	\$5,500.00
	B. Clarke (June 17-18, 2 days @\$250.00)	\$500.00
	G. Karstensen (June 17-18, 2 days @\$250.00)	\$500.00
Trucks (4x4)	Truck Rentals	\$2,170.00
Powersaw Rental	4 days @\$35.00	\$140.00
Fuel		\$1,188.86
Accomodation		\$750.00
Food/Meals		\$1,301.72
Analyses	Eco-Tech Laboratories Ltd (794 soil samples)	\$11,235.10
Miscellaneous	Sample bags, flagging, tags etc	\$192.50
Shipping		\$44.83
Report Preparation		\$2,500.00
	TOTAL	\$31,873.01

10.0 REFERENCES

- Augsten, B., (2005): *Assessment Report: 2005 Report on Trenching on the Barnes Creek Property*
- Augsten, B., (2005): *Assessment Report: 2004 Summary of Exploration on the Barnes Creek Property*
- Augsten, B., (2004): *Assessment Report: 2003 Soil Geochemistry Report on the Barnes Creek Property.*
- Augsten, B., (2004): *Assessment Report: 2003 Trenching Report on the Barnes Creek Property.*
- Burton, A. (1983): *Assessment Report: 1983 Geochemical and Heavy Sediment Survey, Keefer and Crystal Claims, Keefer Lake Area, Vernon Mining Division. Assessment Report #11645.*
- Beaty, R.J. et al., (1983) *Report on a Geochemical Survey of the Peak-Reka-Hold Claim Group. Assessment Report #11,752.*
- Caltagirone, A.T. (1988): *Assessment Report on the Snow Property, Vernon and Slocan Mining Divisions, British Columbia. Assessment Report #18079.*
- Englund, R.J. (1990): *Assessment Report on the Bowl Claim Group, Keefer Lake Area, for M.E. Boe; Report #20,445*
- Höy,T., et al., (1994): *Kootenay Area (82E,F,G,J,L,M,N,O; 83C,D); BC Ministry of Energy, Mines and Petroleum Resources, Open File 1994-8.*
- Jones, A.G. (1959): *Vernon Map Area British Columbia; Geological Survey of Canada, Memoir 296*
- McGoran, J. (1982): *Geochemical Report on Keefer Claim. Assessment Report #10871.*
- Nelles, David M. (1983): *Assessment Report on Geological, Prospecting and Geochemical Surveys, Zag 1 & 2 Mineral Claims, for Golden Porphyrite Ltd.; Report # 12338*
- Okulitch, A.V. (1979): *Geology and Mineral Occurrences of the Thompson-Shuswap-Okanagan Region, south-central British Columbia, Geological Survey of Canada, Open File 637*

- Thompson, R.I., Glombick, P., and Lemieux, Y. (compilers) (2003):
Geology, Eureka Mountain, British Columbia; Geological Survey of Canada, Open File 4370, scale 1:50,000.
- Tully, Donald W. (1981): *Assessment Report on the 1981 Program of Diamond Drilling, Lynx Claim (16 units), Trapp Creek-Kettle River, Keefer lake Area; Report #10,530*
- Wynne, F.L. (1983): *Assessment Report, Keefer Lake Properties, Report on a Geochemical Soil Survey on the Aron 1-7, 10, 13-18, Ban 1-3, Eureka 1-4, 6, 7, Kee 1-6 and Thunder 1,2 Claims; Vernon and Slocan Mining Divisions, B.C. Assessment Report #11817.*
- MINFILE: British Columbia Mineral Occurrence database.
- RGS: British Columbia geochemical database
- MAPPLACE: interactive site for geoscience data for British Columbia.

11.0 CERTIFICATE of AUTHOR

I, Bernhardt Augsten, P. Geo., do hereby certify that:

1. *I am currently self-employed as a consulting geologist resident at:*

*5936 Stafford Rd.
Nelson, BC
V1L 6P3*
2. *I graduated with a degree in Geology, BSc Hons, from Carleton University in 1985.*
3. *I am a member of the Association of Professional Engineers and Geoscientists of British Columbia.*
4. *I have worked as an exploration geologist since my graduation from university.*
5. *I have read the definition of “qualified person” set out in National Instrument 43-101 (“NI 43-101”) and certify that by reason of my education, affiliation with a professional association (as defined in NI 43-101) and past relevant work experience, I fulfill the requirements to be a “qualified person” for the purposes of NI 43-101.*
6. *I am a part owner of the Barnes Creek Property and as such have had a long standing involvement with the Property.*

APPENDIX I
SOIL ANALYSES

23-Jun-05

ECO TECH LABORATORY LTD.
10041 Dallas Drive
KAMLOOPS, B.C.
V2C 6T4

Phone: 250-573-5700
Fax : 250-573-4557

ICP CERTIFICATE OF ANALYSIS AK 2005-519

COLUMBIA YUKON EXPLORATIONS INC.
5936 Stafford Road
Nelson, BC
V1L 6P3

ATTENTION: Bernie Augsten / Gillian Feyer

No. of samples received: 304

Sample type: Soil

Project #: Barnes Creek

Shipment #: Not Indicated

Samples submitted by: Bernie Augsten

Values in ppm unless otherwise reported

Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
1	L24N 6900E	5	0.4	2.61	15	95	<5	0.59	<1	20	50	54	4.38	<10	0.73	474	<1	0.02	39	800	34	10	<20	31	0.17	<10	125	<10	11	101
2	L24N 6925E	10	0.2	2.65	35	100	<5	0.15	<1	13	30	31	3.51	<10	0.32	506	<1	0.01	20	860	40	<5	<20	9	0.12	<10	81	<10	8	108
3	L24N 6950E	5	0.5	3.04	65	85	5	0.31	<1	16	32	25	3.79	<10	0.35	303	<1	0.02	27	1140	40	<5	<20	17	0.13	<10	85	<10	6	111
4	L24N 6975E	15	0.2	2.83	40	110	<5	0.19	<1	19	46	42	4.58	<10	0.53	394	2	0.02	33	680	38	<5	<20	12	0.14	<10	108	<10	9	141
5	L24N 7000E	10	0.3	2.08	25	115	5	0.50	<1	18	32	32	3.21	<10	0.29	1001	<1	0.02	29	1220	30	<5	<20	33	0.12	<10	71	<10	7	125
6	L24N 7025E	10	0.4	2.80	60	80	5	0.16	<1	14	23	24	3.29	<10	0.22	534	<1	0.01	16	1450	38	<5	<20	10	0.12	<10	75	<10	5	111
7	L24N 7050E	25	0.5	3.41	65	60	<5	0.20	<1	19	25	38	4.46	<10	0.37	306	<1	0.02	19	870	46	<5	<20	12	0.16	<10	109	<10	7	98
8	L24N 7075E	10	0.4	2.81	40	95	<5	0.53	<1	21	31	33	4.18	<10	0.25	711	<1	0.01	44	1710	38	<5	<20	33	0.11	<10	70	<10	6	94
9	L24N 7100E	10	0.2	2.61	25	75	5	0.39	<1	19	26	31	4.06	<10	0.21	660	1	0.01	32	1510	36	5	<20	25	0.11	<10	67	<10	7	93
10	L24N 7125E	45	0.4	2.42	110	65	<5	0.51	<1	21	47	25	4.57	<10	0.24	422	9	0.02	56	1160	34	10	<20	30	0.14	<10	68	<10	8	98
11	L24N 7150E	15	0.5	2.54	65	80	<5	0.34	<1	13	30	18	3.11	<10	0.17	316	<1	0.01	26	940	36	<5	<20	21	0.12	<10	66	<10	6	106
12	L24N 7175E	15	0.5	2.37	135	70	<5	0.25	<1	17	32	31	4.11	<10	0.28	381	1	0.01	27	1030	32	<5	<20	14	0.11	<10	94	<10	8	140
13	L24N 7200E	5	0.5	2.56	25	65	<5	0.38	<1	12	20	20	4.18	<10	0.20	179	<1	0.01	19	920	36	<5	<20	20	0.13	<10	74	<10	5	104
14	L24N 7225E	70	0.9	2.83	165	60	<5	0.26	<1	15	19	25	3.47	<10	0.23	290	<1	0.01	22	1040	40	10	<20	21	0.11	<10	62	<10	10	109
15	L24N 7250E	25	0.6	3.31	95	55	<5	0.32	<1	17	32	32	3.48	<10	0.24	231	<1	0.01	28	750	46	<5	<20	18	0.14	<10	72	<10	15	133
16	L24N 7275E	20	0.7	2.06	80	75	5	0.78	<1	22	26	40	4.14	<10	0.30	1180	2	0.01	30	1090	32	5	<20	48	0.09	<10	81	<10	4	90
17	L24N 7300E	35	0.3	2.51	160	60	5	0.31	<1	20	43	39	4.10	<10	0.32	635	3	0.01	59	1120	36	10	<20	16	0.11	<10	78	<10	9	97
18	L24N 7325E	25	0.4	2.56	130	70	<5	0.43	<1	18	33	38	4.08	<10	0.30	317	<1	0.01	26	1070	34	<5	<20	27	0.11	<10	91	<10	4	97
19	L24N 7350E	10	0.3	2.59	40	65	<5	0.23	<1	14	21	50	4.59	<10	0.34	293	1	0.01	16	1160	36	<5	<20	18	0.13	<10	126	<10	6	95
20	L24N 7375E	15	0.4	2.21	35	60	<5	0.27	<1	18	23	47	4.66	<10	0.36	498	<1	0.01	16	1510	32	<5	<20	22	0.14	<10	121	<10	4	97
21	L24N 7400E	10	0.4	2.39	20	85	5	0.21	<1	13	12	34	3.40	<10	0.17	296	<1	0.01	10	1560	36	<5	<20	16	0.12	<10	84	<10	5	81
22	L24N 7425E	10	0.5	2.71	30	75	<5	0.32	<1	21	22	57	4.55	<10	0.48	451	<1	0.01	22	1450	40	<5	<20	23	0.14	<10	120	<10	7	112
23	L24N 7450E	5	0.5	2.23	25	60	<5	0.24	<1	12	16	41	3.83	<10	0.23	227	<1	0.01	12	1300	36	<5	<20	19	0.14	<10	98	<10	4	69
24	L24N 7475E	5	0.5	2.41	45	100	<5	0.13	<1	15	22	23	3.89	<10	0.25	373	2	<0.01	18	1420	42	<5	<20	7	0.08	<10	65	<10	5	179
25	L25N 6900E	365	1.1	2.11	300	115	<5	0.92	<1	22	32	87	5.64	<10	0.62	595	1	0.02	47	830	32	45	<20	34	0.10	<10	114	<10	15	177
26	L25N 6925E	10	1.0	2.30	125	110	<5	1.15	<1	19	36	53	4.04	<10	0.47	1122	3	0.02	31	900	34	<5	<20	30	0.09	<10	87	<10	16	130
27	L25N 6950E	10	0.8	2.58	165	55	<5	0.67	1	10	22	81	2.28	<10	0.15	574	<1	0.02	26	600	38	<5	<20	17	0.09	<10	38	<10	19	81
28	L25N 6975E	10	0.7	2.46	105	100	<5	0.17	<1	15	38	41	4.89	<10	0.38	196	1	0.01	26	380	38	<5	<20	10	0.14	<10	106	<10	11	153
29	L25N 7025E	10	1.6	2.36	65	90	5	0.89	1	18	37	34	4.13	<10	0.49	460	<1	0.02	34	610	36	<5	<20	26	0.12	<10	80	<10	18	177
30	L25N 7050E	15	1.6	2.38	55	90	<5	0.83	1	15	30	37	3.95	<10	0.42	860	2	0.02	24	810	34	<5	<20	21	0.09	<10	84	<10	18	128

23-Jun-05

ECO TECH LABORATORY LTD.

ICP CERTIFICATE OF ANALYSIS AK 2005-519

COLUMBIA YUKON EXPLORATIONS INC.

Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
-------	-------	---------	----	------	----	----	----	------	----	----	----	----	------	----	------	----	----	------	----	---	----	----	----	----	------	---	---	---	---	----

31	L25N 7075E	5	0.6	1.98	35	115	<5	0.12	1	15	32	23	4.14	<10	0.32	523	1	0.01	22	1390	30	<5	<20	6	0.11	<10	85	<10	4	145
32	L25N 7100E	5	0.8	1.92	45	145	5	0.36	1	15	30	24	3.83	<10	0.40	1697	2	0.01	25	900	30	<5	<20	11	0.11	<10	79	<10	6	200
33	L25N 7125E	5	1.2	2.46	45	90	<5	0.20	<1	13	24	19	3.17	<10	0.28	811	<1	0.01	24	970	38	<5	<20	8	0.11	<10	59	<10	9	159
34	L25N 7150E	5	1.0	2.48	50	75	<5	0.40	<1	15	29	25	3.65	<10	0.38	281	<1	0.01	30	640	38	<5	<20	14	0.11	<10	68	<10	12	158
35	L25N 7175E	5	1.4	3.27	80	90	<5	0.65	2	14	27	41	3.48	<10	0.32	1225	2	0.02	34	790	50	<5	<20	17	0.12	<10	72	<10	26	176
36	L25N 7200E	10	0.5	2.73	60	85	<5	0.90	<1	16	21	43	4.21	<10	0.41	498	1	0.02	20	780	40	<5	<20	27	0.12	<10	92	<10	19	137
37	L25N 7225E	15	0.4	3.19	90	45	<5	0.80	<1	20	24	46	3.96	<10	0.34	374	<1	0.02	18	760	48	<5	<20	31	0.10	<10	90	<10	17	97
38	L25N 7250E	10	<0.2	1.62	60	85	<5	0.36	<1	17	47	31	4.70	<10	0.81	429	1	0.02	32	690	26	<5	<20	19	0.13	<10	104	<10	8	180
39	L25N 7275E	5	0.3	3.15	25	65	5	0.08	<1	9	12	15	3.34	<10	0.12	185	2	0.01	8	930	50	<5	<20	5	0.11	<10	60	<10	7	111
40	L25N 7300E	10	0.5	2.91	40	65	<5	0.24	<1	12	11	31	3.79	<10	0.18	297	3	0.01	10	1260	46	<5	<20	19	0.11	<10	72	<10	6	113
41	L25N 7325E	15	0.4	1.16	15	50	<5	0.08	<1	8	8	11	3.35	<10	0.07	334	1	0.01	8	850	26	<5	<20	7	0.11	<10	62	<10	2	58
42	L25N 7350E	5	0.3	2.85	20	75	<5	0.21	<1	18	19	30	3.81	<10	0.23	324	2	0.01	16	1490	44	<5	<20	17	0.13	<10	86	<10	6	88
43	L25N 7375E	5	0.4	2.11	30	65	<5	0.23	<1	13	23	40	3.62	<10	0.29	260	1	0.01	19	1070	34	<5	<20	16	0.13	<10	90	<10	8	93
44	L25N 7400E	20	0.2	2.29	65	75	5	0.31	<1	17	17	41	3.60	<10	0.34	658	1	0.01	15	2310	36	<5	<20	20	0.11	<10	91	<10	5	97
45	L25N 7425E	20	0.3	2.41	80	60	5	0.31	<1	19	55	42	3.84	<10	0.45	344	2	0.01	54	990	36	<5	<20	21	0.13	<10	104	<10	10	111
46	L25N 7450E	85	0.5	2.90	165	105	<5	0.42	<1	24	61	50	4.85	<10	0.82	724	<1	0.02	52	1150	44	<5	<20	34	0.15	<10	145	<10	9	130
47	L25N 7475E	15	0.4	2.73	75	100	<5	0.44	<1	23	53	52	4.59	<10	0.75	732	<1	0.02	40	1090	42	<5	<20	34	0.18	<10	144	<10	13	134
48	L26N 6900E	10	0.8	2.09	35	95	<5	0.10	<1	15	18	20	3.57	<10	0.18	479	2	<0.01	17	1930	38	<5	<20	4	0.08	<10	51	<10	4	181
49	L26N 6925E	5	0.4	2.16	35	140	5	0.07	1	14	22	18	4.58	<10	0.23	519	4	<0.01	19	4440	38	<5	<20	5	0.08	<10	63	<10	1	191
50	L26N 6950E	5	0.7	2.07	20	125	<5	0.08	<1	8	13	9	2.63	<10	0.08	1355	<1	0.01	9	2070	40	<5	<20	4	0.09	<10	42	<10	2	145
51	L26N 6975E	5	0.7	2.43	25	105	5	0.09	<1	12	15	13	3.15	<10	0.09	546	3	<0.01	10	1080	42	<5	<20	3	0.07	<10	48	<10	2	154
52	L26N 7000E	5	0.7	2.61	25	90	<5	0.05	<1	14	15	18	3.02	<10	0.11	608	<1	0.01	13	1460	44	<5	<20	2	0.11	<10	42	<10	11	123
53	L26N 7025E	5	0.5	2.42	25	100	5	0.10	<1	10	14	12	2.77	<10	0.13	409	1	0.01	12	1590	42	<5	<20	5	0.07	<10	41	<10	2	149
54	L26N 7050E	5	0.3	1.16	35	90	<5	0.07	<1	8	17	17	3.42	<10	0.17	222	4	<0.01	13	890	24	<5	<20	2	0.06	<10	60	<10	1	122
55	L26N 7075E	10	0.3	2.48	165	100	<5	0.75	<1	18	37	42	3.71	<10	0.49	863	<1	0.02	26	1310	42	<5	<20	25	0.11	<10	95	<10	15	203
56	L26N 7100E	10	0.3	2.68	185	125	<5	0.98	<1	30	75	95	5.80	<10	1.10	1505	1	0.03	53	1120	40	<5	<20	44	0.14	<10	169	<10	25	273
57	L26N 7125E	10	0.5	2.26	125	150	<5	1.59	1	27	72	89	5.37	<10	1.15	1538	<1	0.04	47	1330	34	<5	<20	54	0.12	<10	166	<10	22	213
58	L26N 7150E	10	0.2	2.42	150	110	5	1.18	<1	25	84	77	5.64	<10	1.17	761	1	0.03	48	670	34	<5	<20	44	0.14	<10	174	<10	16	183
59	L26N 7175E	15	0.4	2.51	140	155	<5	1.37	<1	28	78	97	5.84	<10	1.22	1293	<1	0.04	54	1190	36	<5	<20	53	0.14	<10	184	<10	25	181
60	L26N 7200E	5	0.3	2.05	15	100	<5	0.38	<1	21	110	29	4.66	<10	0.59	621	<1	0.02	83	940	32	<5	<20	19	0.17	<10	113	<10	11	131
61	L26N 7225E	10	0.4	3.44	95	175	5	0.83	<1	24	58	54	5.18	<10	0.95	1387	<1	0.05	48	920	52	<5	<20	29	0.21	<10	139	<10	18	221
62	L26N 7250E	10	0.2	2.88	110	245	<5	1.06	<1	34	75	117	5.97	<10	1.13	840	<1	0.03	82	970	40	<5	<20	58	0.18	<10	166	<10	21	130
63	L26N 7275E	10	0.4	2.53	250	140	<5	1.50	<1	19	64	56	4.08	<10	0.68	1760	<1	0.03	68	940	38	<5	<20	39	0.10	<10	119	<10	15	141
64	L26N 7300E	75	0.2	2.79	150	140	5	0.36	<1	22	64	46	4.54	<10	0.81	436	<1	0.02	51	690	42	<5	<20	22	0.18	<10	137	<10	14	140
65	L26N 7325E	10	0.3	2.44	100	160	<5	1.12	<1	21	61	50	4.38	<10	0.73	1923	<1	0.02	42	1030	40	<5	<20	32	0.14	<10	132	<10	14	186
66	L26N 7350E	120	0.9	2.30	195	95	<5	0.70	<1	23	100	45	4.75	<10	0.76	557	<1	0.01	64	1160	36	<5	<20	47	0.11	<10	164	<10	8	145
67	L26N 7375E	5	0.4	2.61	20	85	5	0.30	1	15	24	23	3.24	<10	0.29	407	<1	0.02	15	750	42	<5	<20	23	0.14	<10	79	<10	9	126
68	L26N 7400E	15	<0.2	2.73	70	80	5	0.35	<1	17	27	17	3.73	<10	0.37	369	<1	0.02	15	1080	44	<5	<20	21	0.16	<10	85	<10	12	118
69	L26N 7425E	35	0.2	2.39	60	135	5	0.25	<1	18	42	32	4.79	<10	0.65	606	<1	0.02	25	1420	38	<5	<20	17	0.16	<10	138	<10	7	176
70	L26N 7450E	10	1.1	2.31	55	115	<5	0.13	<1	19	35	28	4.49	<10	0.37	629	1	0.01	25	1050	40	<5	<20	7	0.13	<10	89	<10	8	235

23-Jun-05

ECO TECH LABORATORY LTD.

ICP CERTIFICATE OF ANALYSIS AK 2005-519

COLUMBIA YUKON EXPLORATIONS INC.

Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn

<tbl_r

75	L27N 6900E	<5	0.4	3.55	10	205	10	0.20	<1	18	55	47	4.13	<10	0.89	1245	<1	0.04	35	1460	38	<5	<20	17	0.16	<10	134	<10	6	109
76	L27N 6925E	5	0.2	3.59	35	130	<5	0.42	<1	20	62	73	4.79	<10	1.25	516	<1	0.04	35	540	34	<5	<20	30	0.17	<10	173	<10	9	96
77	L27N 6950E	<5	0.3	3.84	15	190	5	0.23	1	18	46	56	4.16	<10	0.99	1241	<1	0.03	36	1550	36	<5	<20	22	0.16	<10	140	<10	4	117
78	L27N 6975E	<5	0.4	3.67	20	150	10	0.28	<1	20	44	62	4.11	<10	0.87	1127	<1	0.03	34	1280	34	<5	<20	23	0.14	<10	134	<10	5	112
79	L27N 7000E	<5	0.2	3.63	15	200	5	0.30	<1	19	57	59	4.32	<10	1.03	609	<1	0.03	36	990	34	<5	<20	24	0.17	<10	161	<10	4	141
80	L27N 7025E	<5	0.3	3.90	15	155	5	0.48	1	23	67	99	4.74	<10	1.43	794	<1	0.05	48	590	34	<5	<20	35	0.19	<10	183	<10	12	138
81	L27N 7050E	<5	0.3	3.77	20	140	5	0.52	2	20	52	80	4.52	<10	1.20	1518	<1	0.04	46	670	36	<5	<20	35	0.17	<10	163	<10	16	149
82	L27N 7075E	<5	0.2	3.82	15	160	5	0.25	<1	19	66	57	4.35	<10	1.13	569	<1	0.03	40	800	36	<5	<20	22	0.18	<10	158	<10	8	101
83	L27N 7100E	5	0.2	3.52	30	260	5	0.56	<1	22	70	78	4.78	<10	1.31	1134	<1	0.04	47	1120	34	<5	<20	47	0.16	<10	168	<10	10	98
84	L27N 7125E	<5	0.8	2.50	45	130	5	0.08	1	18	31	48	4.80	<10	0.55	432	4	0.01	27	550	32	<5	<20	6	0.08	<10	91	<10	<1	143
85	L27N 7150E	<5	0.3	3.13	175	110	<5	0.33	<1	21	61	83	4.84	<10	1.03	741	<1	0.03	38	410	34	<5	<20	26	0.15	<10	156	<10	12	137
86	L27N 7175E	<5	0.4	3.45	55	100	<5	0.13	<1	16	23	24	3.28	<10	0.33	397	<1	0.02	14	800	38	<5	<20	9	0.13	<10	73	<10	3	101
87	L27N 7200E	<5	0.3	3.79	60	165	10	0.25	<1	19	46	48	4.08	<10	0.91	798	<1	0.02	30	1230	36	<5	<20	21	0.16	<10	140	<10	4	110
88	L27N 7225E	<5	0.3	3.50	35	115	<5	0.29	<1	18	31	41	3.97	<10	0.64	600	<1	0.02	23	1110	34	<5	<20	23	0.12	<10	137	<10	3	92
89	L27N 7250E	<5	0.2	3.79	35	130	10	0.37	<1	19	50	56	4.39	<10	1.03	431	<1	0.03	30	740	34	<5	<20	27	0.15	<10	156	<10	5	100
90	L27N 7275E	<5	0.3	3.38	40	165	<5	0.22	<1	17	38	43	3.99	<10	0.74	459	<1	0.03	21	1020	34	<5	<20	18	0.17	<10	135	<10	4	112
91	L27N 7300E	10	0.2	4.12	75	135	5	0.37	<1	23	57	88	4.88	<10	1.23	413	<1	0.03	42	720	34	<5	<20	30	0.18	<10	173	<10	7	104
92	L27N 7325E	5	0.4	3.69	190	125	<5	0.86	<1	21	75	91	4.46	<10	1.25	806	<1	0.03	53	710	32	<5	<20	51	0.14	<10	166	<10	14	101
93	L27N 7350E	<5	0.3	3.26	30	135	5	0.15	<1	16	56	34	3.69	<10	0.65	679	<1	0.02	37	1530	34	<5	<20	11	0.13	<10	120	<10	3	98
94	L27N 7375E	<5	0.5	2.73	25	165	<5	0.21	2	16	39	37	3.72	<10	0.59	1545	<1	0.03	24	950	28	<5	<20	18	0.13	<10	122	<10	4	157
95	L27N 7400E	<5	0.3	3.23	15	130	<5	0.23	1	17	46	49	4.01	<10	0.85	819	<1	0.02	26	790	30	<5	<20	22	0.14	<10	140	<10	5	127
96	L27N 7425E	5	0.5	3.48	20	100	5	0.23	<1	14	28	46	4.03	<10	0.69	618	<1	0.02	14	1040	36	<5	<20	22	0.15	<10	134	<10	2	82
97	L27N 7450E	<5	0.2	3.33	5	145	<5	0.29	<1	18	42	51	4.10	<10	0.87	918	<1	0.02	23	1320	30	<5	<20	26	0.13	<10	157	<10	2	119
98	L27N 7475E	5	0.3	3.30	20	130	<5	0.42	<1	20	55	73	4.99	<10	1.14	668	<1	0.03	25	1450	30	<5	<20	38	0.14	<10	177	<10	2	98
99	L27N 7500E	<5	0.3	3.58	15	85	10	0.50	<1	20	39	56	4.28	<10	1.00	1000	<1	0.03	28	1030	32	<5	<20	42	0.15	<10	143	<10	8	122
100	L27N 7525E	75	0.2	2.38	60	75	<5	0.11	<1	11	18	26	3.92	<10	0.38	287	3	0.01	13	1060	28	<5	<20	8	0.07	<10	73	<10	1	104
101	L27N 7550E	15	0.3	2.70	40	95	<5	0.09	<1	13	16	18	3.34	<10	0.30	780	1	0.01	8	1390	28	<5	<20	5	0.06	<10	67	<10	<1	83
102	L27N 7575E	5	0.5	2.66	55	130	<5	0.11	<1	15	24	39	3.76	<10	0.49	640	1	0.01	21	740	30	<5	<20	7	0.09	<10	84	<10	3	160
103	L27N 7600E	5	0.7	2.58	35	120	5	0.09	1	12	16	25	2.94	<10	0.27	889	2	0.02	16	850	30	<5	<20	4	0.07	<10	57	<10	5	150
104	L27N 7625E	<5	0.8	2.23	35	100	<5	0.08	1	12	19	32	3.59	<10	0.40	457	4	0.01	18	760	28	<5	<20	5	0.06	<10	63	<10	<1	137
105	L27N 7650E	5	0.5	2.13	30	130	<5	0.07	1	12	17	29	3.08	<10	0.34	975	3	0.01	16	1000	28	<5	<20	5	0.06	<10	55	<10	<1	137
106	L27N 7675E	5	0.7	2.24	30	135	<5	0.06	1	11	18	28	3.25	<10	0.31	871	2	0.01	14	1010	30	<5	<20	4	0.07	<10	59	<10	4	124
107	L32N 7675E	20	0.4	2.61	175	75	10	0.33	<1	21	26	47	3.82	<10	0.68	926	<1	0.02	20	990	34	<5	<20	20	0.10	<10	89	<10	16	125
108	L32N 7700E	140	1.5	3.41	95	60	<5	0.44	<1	16	17	23	3.13	<10	0.48	756	<1	0.01	11	1080	54	<5	<20	37	0.10	<10	78	<10	8	119
109	L32N 7725E	25	0.2	2.77	55	105	10	0.43	<1	16	24	30	3.60	<10	0.67	869	<1	0.01	17	1010	40	<5	<20	44	0.11	<10	83	<10	4	135
110	L32N 7750E	10	0.4	2.14	70	85	<5	0.19	<1	18	29	53	4.09	<10	0.83	741	2	0.01	30	840	24	<5	<20	11	0.09	<10	83	<10	5	132

23-Jun-05

ECO TECH LABORATORY LTD.

ICP CERTIFICATE OF ANALYSIS AK 2005-519

COLUMBIA YUKON EXPLORATIONS INC.

Et #	Tag #	Au(ppb)	Aq	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
111	L33N 7675E	25	0.6	2.83	285	95	<5	0.58	<1	15	20	36	3.13	<10	0.46	1128	<1	0.02	13	700	32	10	<20	38	0.10	<10	74	<10	11	100
112	L33N 7700E	15	0.3	3.16	80	70	<5	0.39	<1	10	13	26	2.63	<10	0.35	391	<1	0.02	9	940	34	<5	<20	37	0.08	<10	58	<10	1	73
113	L33N 7725E	20	0.4	3.13	95	80	<5	0.28	<1	12	15	24	2.71	<10	0.36	475	<1	0.02	8	980	34									

118	L3350N 7625E	30	0.5	2.13	245	90	5	0.22	<1	18	27	33	4.20	<10	0.66	985	1	0.01	11	1130	26	40	<20	17	0.09	<10	103	<10	<1	94
119	L3350N 7650E	20	0.2	2.37	145	90	<5	0.27	<1	15	18	27	3.40	<10	0.42	1207	<1	0.02	11	1130	30	10	<20	33	0.10	<10	89	<10	4	90
120	L3350N 7675E	30	0.4	2.28	130	125	5	0.18	<1	17	27	38	3.86	<10	0.61	1052	2	0.01	21	1430	26	15	<20	15	0.09	<10	90	<10	2	126
121	L3350N 7700E	30	0.3	2.22	200	105	<5	0.22	<1	17	28	36	4.58	<10	0.73	1064	<1	0.01	16	1290	26	45	<20	17	0.11	<10	118	<10	<1	111
122	L34N 6900E	55	0.5	2.92	60	60	<5	0.10	<1	10	11	24	2.35	<10	0.17	388	<1	0.02	8	830	34	<5	<20	5	0.10	<10	50	<10	1	55
123	L34N 6925E	10	0.2	2.79	45	55	5	0.13	<1	14	17	24	3.11	<10	0.28	789	<1	0.02	11	1540	32	<5	<20	8	0.10	<10	68	<10	<1	65
124	L34N 6950E	175	0.3	2.24	100	105	<5	0.10	<1	10	14	22	2.77	<10	0.22	441	<1	0.02	9	960	30	<5	<20	6	0.09	<10	62	<10	<1	62
125	L34N 6975E	10	0.2	2.11	40	95	<5	0.15	<1	10	17	23	3.12	<10	0.24	541	<1	0.02	11	590	30	<5	<20	10	0.11	<10	77	<10	2	70
126	L34N 7000E	30	0.3	2.36	125	50	<5	0.50	<1	13	17	29	2.68	<10	0.29	656	<1	0.02	9	540	32	<5	<20	22	0.09	<10	63	<10	15	52
127	L34N 7025E	295	0.3	2.22	95	100	5	0.39	<1	12	15	27	3.72	<10	0.44	803	1	0.02	8	570	30	15	<20	63	0.08	<10	85	<10	1	65
128	L34N 7050E	40	1.0	3.45	845	60	<5	0.90	<1	15	14	79	3.29	<10	0.30	531	1	0.02	15	800	42	<5	<20	40	0.10	<10	63	<10	52	83
129	L34N 7075E	50	1.2	3.36	850	55	<5	0.89	<1	12	10	82	2.59	<10	0.22	886	2	0.02	11	790	38	5	<20	37	0.07	<10	46	<10	49	61
130	L34N 7100E	30	1.1	3.57	675	95	<5	0.43	<1	8	11	33	2.33	<10	0.20	270	<1	0.02	9	1320	38	<5	<20	29	0.08	<10	40	<10	25	83
131	L34N 7125E	40	0.3	2.93	400	75	<5	0.35	<1	13	15	33	3.73	<10	0.46	527	1	0.01	9	770	32	<5	<20	28	0.10	<10	83	<10	11	88
132	L34N 7150E	55	0.4	2.77	445	95	5	0.19	<1	15	17	36	4.09	<10	0.51	864	<1	0.01	11	870	34	5	<20	14	0.12	<10	97	<10	11	90
133	L34N 7175E	55	0.4	2.72	325	110	5	0.26	<1	14	18	32	3.89	<10	0.47	462	<1	0.02	13	900	32	<5	<20	18	0.11	<10	87	<10	5	94
134	L34N 7200E	105	0.4	2.57	240	105	<5	0.26	<1	14	21	29	3.91	<10	0.49	589	<1	0.01	13	910	30	<5	<20	19	0.12	<10	90	<10	2	101
135	L34N 7225E	75	0.3	2.70	215	110	5	0.28	<1	16	20	26	3.60	<10	0.42	827	<1	0.02	11	710	32	10	<20	22	0.12	<10	81	<10	2	98
136	L34N 7250E	80	0.3	2.00	150	100	<5	0.20	<1	10	19	23	3.38	<10	0.50	453	<1	0.02	9	610	28	<5	<20	14	0.08	<10	75	<10	<1	72
137	L34N 7275E	25	0.4	2.55	205	80	<5	0.26	<1	11	13	22	2.44	<10	0.18	1040	<1	0.02	8	810	36	10	<20	13	0.10	<10	50	<10	10	71
138	L34N 7300E	15	0.3	2.65	45	65	<5	0.06	<1	8	13	13	2.87	<10	0.16	400	<1	0.01	6	790	34	<5	<20	2	0.12	<10	59	<10	<1	62
139	L34N 7325E	25	0.2	2.00	80	150	<5	0.18	<1	12	24	24	3.59	<10	0.44	1223	<1	0.02	14	660	32	<5	<20	15	0.13	<10	89	<10	<1	99
140	L34N 7350E	20	0.6	2.31	320	95	<5	0.15	<1	11	20	21	4.20	<10	0.39	477	<1	0.02	10	710	28	<5	<20	18	0.10	<10	82	<10	<1	113
141	L34N 7375E	5	0.8	2.45	845	100	<5	0.78	<1	20	33	78	4.05	20	0.75	1873	2	0.02	18	870	26	35	<20	46	0.09	<10	104	<10	48	104
142	L34N 7400E	5	0.5	2.33	145	110	5	0.17	<1	16	26	34	3.79	<10	0.54	642	2	0.02	19	830	26	<5	<20	15	0.10	<10	81	<10	7	131
143	L34N 7425E	10	0.4	2.01	70	135	<5	0.16	1	17	29	39	4.64	<10	0.62	556	2	0.02	24	850	28	<5	<20	14	0.11	<10	98	<10	5	125
144	L34N 7450E	5	0.8	1.90	120	90	5	0.26	<1	17	34	68	5.23	<10	0.87	475	5	0.01	35	1110	24	<5	<20	18	0.09	<10	100	<10	4	135
145	L34N 7475E	10	0.5	2.16	135	95	5	0.23	<1	18	39	60	4.75	<10	0.93	465	3	0.01	33	690	24	<5	<20	18	0.09	<10	109	<10	6	129
146	L34N 7500E	10	0.2	1.40	35	100	<5	0.29	<1	15	31	40	2.91	<10	0.68	433	<1	0.02	28	670	20	<5	<20	23	0.10	<10	62	<10	12	87
147	L34N 7525E	10	0.4	1.52	30	95	5	0.24	<1	13	32	30	2.73	<10	0.63	374	<1	0.02	23	760	22	<5	<20	20	0.09	<10	60	<10	9	74
148	L34N 7550E	5	<0.2	2.13	360	115	5	0.21	<1	16	24	29	4.69	<10	0.66	694	4	0.01	15	770	28	135	<20	24	0.06	<10	104	<10	4	113
149	L34N 7575E	5	0.3	1.65	140	125	5	0.12	<1	12	27	33	3.89	<10	0.57	440	2	<0.01	21	740	24	35	<20	12	0.08	<10	82	<10	3	117
150	L34N 7600E	10	0.8	1.96	260	165	<5	0.20	<1	20	21	38	5.70	<10	0.70	1159	3	0.01	11	2330	24	60	<20	20	0.13	<10	140	<10	4	121

23-Jun-05

ECO TECH LABORATORY LTD.

ICP CERTIFICATE OF ANALYSIS AK 2005-519

COLUMBIA YUKON EXPLORATIONS INC.

Et #	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
151	L34N 7625E	10	1.2	1.97	20	120	<5	0.28	7	23	16	63	5.06	<10	0.35	1293	16	0.01	56	1110	26	<5	<20	30	0.07	<10	102	<10	7	386
152	L34N 7650E	10	2.5	2.06	25	150	<5	0.30	7	28	19	82	4.93	<10	0.24	1531	14	0.01	43	1850	34	<5	<20	38	0.07	<10	128	<10	8	326
153	L34N 7675E	20	1.1	2.41	160	125	<5	0.33	2	21	28	62	4.30	<10	0.54	738	4	0.02	47	1210	30	25	<20	30	0.10	<10	118	<10	9	275
154	L34N 7700E	5	0.3	1.91	185	100	<5	0.58	<1	17	27	38	3.65	<10	0.37	981	5	0.01	38	1900	26	25	<20	42	0.07	<10	98	<10	5	160
155	L34N 7725E	5	0.6	2.10	80	110	<5	0.18	<1	15	24	32	3.56	<10	0.41	1305	2	0.01	19	1010	30	<5	<20	20	0.09	<10	86	<10	7	132
156	L34N 7750E	5	1.3	1.91	60	115	<5	0.16	1	13	18	27	3.24	<10	0.31	562	3	0.01	15	1150	34	<5	<2							

161	L35N 6950E	10	0.2	1.77	165	100	<5	0.32	<1	15	32	31	5.14	<10	0.66	332	<1	0.02	11	1150	28	<5	<20	24	0.20	<10	150	<10	8	96
162	L35N 6975E	5	0.2	2.04	65	120	<5	0.27	<1	14	19	26	4.51	<10	0.62	406	<1	0.01	9	1290	26	<5	<20	23	0.18	<10	130	<10	8	92
163	L35N 7000E	5	0.6	2.51	345	75	<5	0.10	<1	13	15	24	3.87	<10	0.40	329	2	0.01	9	780	32	<5	<20	10	0.11	<10	84	<10	7	100
164	L35N 7025E	10	0.5	2.50	455	110	<5	0.20	<1	16	17	33	4.27	<10	0.53	967	<1	0.02	9	1760	30	<5	<20	17	0.12	<10	103	<10	8	115
165	L35N 7050E	5	0.3	1.99	340	145	<5	0.22	<1	19	29	31	6.02	<10	0.79	1741	3	0.01	11	1320	30	<5	<20	19	0.11	<10	157	<10	3	132
166	L35N 7075E	5	0.3	2.00	530	140	<5	0.23	<1	20	26	39	5.99	<10	0.88	870	2	0.01	11	1470	28	<5	<20	15	0.13	<10	152	<10	4	130
167	L35N 7100E	5	0.4	2.09	470	95	5	0.19	<1	21	27	39	5.23	<10	0.68	763	2	0.01	9	1180	28	<5	<20	16	0.11	<10	134	<10	9	113
168	L35N 7125E	5	1.1	2.40	800	115	<5	0.69	<1	20	30	69	5.09	<10	0.84	1099	1	0.02	19	1050	30	<5	<20	27	0.11	<10	143	<10	21	115
169	L35N 7150E	10	0.4	2.15	155	205	<5	0.33	<1	19	38	57	4.82	<10	0.94	1154	2	0.01	34	1150	30	<5	<20	21	0.09	<10	114	<10	3	156
170	L35N 7175E	5	0.3	2.24	195	150	5	0.30	<1	20	43	26	5.78	<10	1.11	750	<1	0.01	14	920	28	<5	<20	15	0.18	<10	174	<10	6	128
171	L35N 7200E	5	0.2	2.19	280	220	5	0.33	<1	25	43	20	6.60	<10	1.29	1716	<1	0.01	12	1430	30	<5	<20	17	0.25	<10	208	<10	10	152
172	L35N 7225E	5	0.4	2.62	610	100	<5	0.19	<1	20	28	42	4.89	<10	0.66	567	1	0.01	15	770	30	<5	<20	21	0.15	<10	117	<10	8	126
173	L35N 7250E	215	0.6	2.27	725	85	5	0.47	<1	21	21	42	4.06	<10	0.53	1245	2	0.02	18	790	32	<5	<20	26	0.08	<10	78	<10	20	121
174	L35N 7275E	5	1.0	2.38	355	105	<5	0.21	<1	14	15	32	3.46	<10	0.31	597	<1	0.01	11	790	34	<5	<20	23	0.09	<10	74	<10	4	108
175	L35N 7300E	5	0.2	1.93	330	165	<5	0.29	<1	12	16	19	3.56	<10	0.31	1063	<1	0.01	9	660	30	<5	<20	23	0.09	<10	75	<10	2	90
176	L35N 7325E	40	0.6	3.09	175	95	<5	0.32	<1	14	15	28	2.92	<10	0.33	648	<1	0.01	12	950	38	<5	<20	27	0.10	<10	60	<10	6	82
177	L35N 7350E	25	0.3	2.08	405	95	<5	0.25	<1	11	14	22	3.26	<10	0.24	662	<1	0.01	9	510	34	<5	<20	18	0.10	<10	67	<10	5	92
178	L35N 7375E	15	0.5	2.71	195	145	<5	0.24	<1	15	23	29	3.83	<10	0.39	855	<1	0.01	16	920	36	<5	<20	22	0.13	<10	83	<10	5	150
179	L35N 7400E	15	0.2	2.49	60	110	<5	0.30	<1	12	20	24	3.02	<10	0.30	921	<1	0.01	13	1170	38	<5	<20	24	0.09	<10	58	<10	4	115
180	L35N 7425E	15	0.5	1.88	15	80	<5	0.30	<1	17	38	71	4.52	<10	0.95	465	1	<0.01	35	1010	26	<5	<20	21	0.09	<10	94	<10	5	134
181	L35N 7450E	10	0.4	2.11	35	110	<5	0.23	<1	17	34	45	4.31	<10	0.73	716	<1	0.01	24	760	30	<5	<20	17	0.11	<10	94	<10	6	144
182	L35N 7475E	10	0.7	1.77	20	120	<5	0.16	<1	15	33	41	4.19	<10	0.71	694	3	<0.01	26	830	28	<5	<20	15	0.08	<10	86	<10	3	143
183	L35N 7500E	55	0.5	1.86	85	115	<5	0.18	1	16	28	36	4.05	<10	0.56	926	2	0.01	22	1650	26	<5	<20	14	0.08	<10	82	<10	3	181
184	L35N 7525E	10	0.6	2.00	10	95	<5	0.18	2	14	44	36	4.05	<10	0.65	352	<1	0.02	42	510	30	<5	<20	15	0.13	<10	88	<10	8	205
185	L35N 7550E	10	0.4	2.17	30	100	<5	0.23	2	15	30	35	3.94	<10	0.51	454	2	0.01	31	700	32	<5	<20	16	0.10	<10	77	<10	7	211
186	L35N 7575E	10	0.8	2.01	15	130	<5	0.29	3	20	28	54	4.40	<10	0.57	680	4	<0.01	43	860	30	<5	<20	26	0.11	<10	93	<10	7	300
187	L35N 7600E	10	1.2	1.98	15	100	5	0.21	3	20	25	56	4.82	<10	0.46	472	5	<0.01	36	950	30	<5	<20	18	0.10	<10	90	<10	6	271
188	L35N 7625E	10	1.5	1.89	15	130	<5	0.16	4	26	21	76	6.41	<10	0.30	1204	15	0.01	56	1610	30	<5	<20	22	0.10	<10	125	<10	6	412
189	L35N 7650E	15	2.4	1.79	5	155	<5	0.17	4	22	18	73	5.81	<10	0.36	2409	12	0.01	44	1190	26	<5	<20	24	0.10	<10	97	<10	6	323
190	L35N 7675E	10	1.8	2.28	<5	130	<5	0.28	3	25	17	89	5.70	<10	0.42	1048	6	<0.01	42	1500	32	<5	<20	29	0.10	<10	78	<10	10	230

23-Jun-05

ECO TECH LABORATORY LTD.

ICP CERTIFICATE OF ANALYSIS AK 2005-519

COLUMBIA YUKON EXPLORATIONS INC.

Et #	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
191	L35N 7700E	15	1.1	2.36	10	160	<5	0.33	2	22	19	61	4.21	<10	0.43	1507	3	0.01	36	930	32	<5	<20	34	0.10	<10	87	<10	9	218
192	L35N 7725E	15	1.2	2.33	30	170	<5	0.27	1	24	20	76	5.04	<10	0.52	921	4	0.01	42	1660	34	<5	<20	31	0.11	<10	90	<10	8	211
193	L35N 7750E	10	1.9	2.45	10	135	<5	0.24	2	23	16	75	6.02	<10	0.48	671	6	0.01	39	1360	36	<5	<20	28	0.12	<10	88	<10	6	200
194	L35N 7775E	15	2.8	1.63	<5	215	<5	0.38	4	18	19	82	7.71	<10	0.24	2110	16	0.01	35	2530	34	<5	<20	47	0.12	<10	127	<10	3	328
195	L35N 7800E	10	1.0	2.05	10	135	<5	0.35	5	21	21	86	6.58	<10	0.32	1018	10	0.01	49	1440	36	<5	<20	43	0.13	<10	106	<10	8	294
196	L36N 6900E	20	0.4	2.10	185	80	<5	0.35	<1	18	36	47	4.15	<10	0.65	658	<1	0.01	25	590	34	<5	<20	24	0.14	<10	125	<10	8	106
197	L36N 6925E	30	<0.2	1.92	205	75	<5	0.17	<1	19	41	50	4.24	<10	0.58	520	<1	0.01	24	680	34	<5	<20	14	0.15	<10	115	<10	6	108
198	L36N 6950E	35	0.2	1.76	125	90	5	0.23	<1	15	31	39	3.88	<10	0.47	394	2	0.01	19	880	26	<5	<20	19	0.13	<10	109	<10	5	88
199	L36N 6975E	30	0.5	2.30	90	85	<5	0.28	<1	17	28	41	3.74	<10	0.42	436	<1	0.01	21											

205	L36N 7125E	15	<0.2	1.93	220	100	<5	0.21	<1	20	39	33	3.75	<10	0.53	475	2	0.01	36	530	30	<5	<20	14	0.10	<10	78	<10	3	95
206	L36N 7150E	10	0.2	2.46	50	70	<5	0.23	<1	21	30	45	3.48	<10	0.41	657	<1	0.01	24	560	30	<5	<20	15	0.11	<10	75	<10	7	82
207	L36N 7175E	20	0.3	2.72	245	100	<5	0.26	<1	19	23	36	3.50	<10	0.46	1095	<1	0.01	22	710	38	<5	<20	18	0.11	<10	79	<10	7	105
208	L36N 7200E	25	0.2	2.01	60	100	<5	0.36	<1	14	24	29	3.51	<10	0.49	1086	<1	0.01	14	790	28	<5	<20	23	0.11	<10	88	<10	5	98
209	L36N 7225E	105	1.1	2.10	175	95	5	0.15	<1	12	17	25	3.19	<10	0.34	1034	<1	<0.01	11	660	30	<5	<20	18	0.11	<10	66	<10	5	86
210	L36N 7250E	25	0.3	2.23	50	80	<5	0.23	<1	15	22	29	3.18	<10	0.48	929	<1	0.01	13	740	32	<5	<20	21	0.10	<10	71	<10	8	88
211	L36N 7275E	45	0.2	2.76	130	115	<5	0.31	<1	18	24	43	3.85	<10	0.56	1104	<1	0.01	16	1200	32	<5	<20	25	0.11	<10	83	<10	6	95
212	L36N 7300E	20	0.2	2.83	50	80	<5	0.27	<1	15	24	38	3.61	<10	0.52	528	<1	0.01	16	730	32	<5	<20	23	0.11	<10	80	<10	7	90
213	L36N 7325E	15	0.3	2.41	70	115	<5	0.30	<1	17	34	32	3.90	<10	0.57	547	<1	0.01	18	690	32	<5	<20	27	0.12	<10	88	<10	6	100
214	L36N 7350E	5	0.4	2.73	30	95	<5	0.22	<1	20	30	48	4.17	<10	0.63	964	<1	0.01	17	940	36	<5	<20	20	0.12	<10	94	<10	8	105
215	L36N 7375E	5	0.2	2.46	30	85	<5	0.20	<1	15	24	29	3.59	<10	0.49	662	<1	0.01	12	710	38	<5	<20	17	0.12	<10	84	<10	7	84
216	L36N 7400E	5	0.2	2.60	45	110	<5	0.44	<1	21	28	40	3.74	<10	0.70	1344	<1	0.01	16	1280	36	<5	<20	41	0.11	<10	94	<10	6	116
217	L36N 7425E	5	0.3	2.05	10	125	<5	0.22	2	19	39	47	4.78	<10	0.89	752	2	<0.01	31	580	28	<5	<20	17	0.10	<10	103	<10	5	150
218	L36N 7450E	5	0.2	1.87	10	145	<5	0.26	2	14	31	32	3.95	<10	0.68	575	2	<0.01	24	800	26	<5	<20	18	0.08	<10	78	<10	3	167
219	L36N 7475E	5	0.5	1.97	15	160	<5	0.19	2	14	31	36	4.14	<10	0.65	693	3	<0.01	24	1270	26	<5	<20	15	0.06	<10	79	<10	3	207
220	L36N 7500E	10	0.5	2.10	30	120	<5	0.27	1	18	34	58	4.33	<10	0.65	827	2	<0.01	30	780	30	<5	<20	20	0.09	<10	91	<10	9	186
221	L36N 7525E	10	0.9	2.26	30	130	<5	0.37	3	20	42	94	4.84	<10	0.87	878	4	0.01	49	990	32	<5	<20	25	0.07	<10	93	<10	17	218
222	L36N 7550E	5	0.6	1.91	15	165	<5	0.34	3	19	36	59	4.52	<10	0.66	1089	7	0.01	49	1390	32	<5	<20	32	0.11	<10	107	<10	8	303
223	L36N 7575E	5	<0.2	2.67	<5	115	<5	0.38	1	21	57	57	5.26	<10	0.95	689	2	0.02	34	1150	28	<5	<20	42	0.13	<10	144	<10	5	162
224	L36N 7600E	5	0.6	2.43	<5	120	<5	0.39	2	24	60	85	5.13	<10	1.00	840	6	0.02	56	590	30	<5	<20	37	0.14	<10	148	<10	8	201
225	L36N 7625E	5	0.4	2.54	10	115	<5	0.27	2	19	44	50	4.32	<10	0.86	614	5	0.02	33	670	30	10	<20	28	0.12	<10	133	<10	7	142
226	L36N 7650E	5	0.8	2.83	<5	105	<5	0.34	2	21	44	85	5.03	<10	0.94	505	6	0.01	47	1010	34	<5	<20	41	0.13	<10	146	<10	8	181
227	L36N 7675E	5	0.6	2.61	15	125	<5	0.30	2	21	44	69	4.90	<10	0.94	718	7	0.01	39	1070	30	<5	<20	36	0.12	<10	138	<10	6	155
228	L36N 7700E	5	1.0	2.37	25	115	<5	0.31	2	19	35	64	4.64	<10	0.77	830	7	0.01	39	1160	34	5	<20	39	0.09	<10	110	<10	4	169
229	L36N 7725E	5	0.8	2.04	30	120	<5	0.12	2	16	24	37	3.70	<10	0.47	1033	6	0.01	25	970	34	<5	<20	15	0.08	<10	73	<10	4	158
230	L36N 7750E	5	0.4	2.30	20	150	<5	0.27	1	19	34	55	4.47	<10	0.81	1124	3	0.01	30	940	32	<5	<20	32	0.10	<10	106	<10	5	180

23-Jun-05

ECO TECH LABORATORY LTD.

ICP CERTIFICATE OF ANALYSIS AK 2005-519

COLUMBIA YUKON EXPLORATIONS INC.

Et #	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
231	L36N 7775E	5	0.3	2.80	15	165	<5	0.47	2	24	50	73	5.23	<10	1.10	1252	7	0.01	43	1180	34	15	<20	56	0.12	<10	149	<10	7	181
232	L36N 7800E	5	0.4	2.35	15	185	<5	0.29	2	25	48	60	4.92	<10	0.82	1424	7	<0.01	53	1390	32	<5	<20	24	0.07	<10	102	<10	6	210
233	L37N 6900E	5	0.3	2.94	15	140	<5	0.28	<1	22	39	72	3.93	<10	0.75	1375	<1	0.02	37	1130	32	<5	<20	31	0.11	<10	123	<10	8	130
234	L37N 6925E	20	0.3	2.98	30	145	<5	0.39	2	21	34	70	3.96	<10	0.76	1399	7	0.02	36	1380	32	15	<20	34	0.09	<10	119	<10	7	119
235	L37N 6950E	10	0.3	2.84	25	150	<5	0.43	<1	24	39	73	4.42	<10	0.91	1462	<1	0.03	35	1180	34	<5	<20	34	0.12	<10	137	<10	8	136
236	L37N 6975E	60	0.7	2.59	70	150	<5	0.32	<1	23	35	71	4.29	<10	0.85	1417	1	0.02	33	1350	32	<5	<20	27	0.09	<10	123	<10	7	145
237	L37N 7000E	15	0.3	3.07	30	105	<5	0.32	<1	22	39	71	4.27	<10	0.92	454	<1	0.02	35	860	36	<5	<20	37	0.14	<10	133	<10	10	132
238	L37N 7025E	5	0.2	2.25	15	130	<5	0.38	<1	16	50	52	4.81	<10	1.09	828	<1	0.03	29	1200	30	<5	<20	28	0.14	<10	155	<10	9	137
239	L37N 7050E	5	0.2	2.64	25	155	<5	0.35	<1	23	47	73	4.93	<10	1.04	1190	<1	0.02	35	1220	32	<5	<20	42	0.14	<10	150	<10	7	145
240	L37N 7075E	5	0.4	2.84	35	110	<5	0.26	<1	22	40	77	4.92	<10	0.98	907	2	0.02	32	830	32	<5	<20	22	0.11	<10	135	<10	9	138
241	L37N 7100E	5	0.9	2.55	50	100	<5	0.23	<1	17	32	50	4.89	<10	0.88	696	2	0.01	21	1150	32	<5	<20	20	0.10	<10	126	<10	4	129
242	L37N 7125E	10	0.3	2.36	55	70	<5	0.49	<1	22	25	40	4.52	<10	0.75	1105	<1	0.02	16	750	30	<5	<20	28	0.12	<10	113	<10	11	110
243	L37N 7150E	10	<0.2	2.16	55	90	<5	0.48	<1	21	30	33	4.25	<10	0.84	1715	<1	0.02	17	890	2									

248	L37N 7275E	10	0.3	2.59	15	80	<5	0.23	<1	17	28	33	3.91	<10	0.67	430	<1	0.01	22	650	36	<5	<20	17	0.16	<10	90	<10	9	104
249	L37N 7300E	5	<0.2	1.82	10	65	<5	0.50	<1	18	27	27	4.35	<10	0.73	683	<1	0.01	17	630	28	<5	<20	26	0.15	<10	97	<10	7	136
250	L37N 7325E	10	0.2	2.18	30	100	<5	0.37	1	19	35	42	4.46	<10	0.80	927	<1	0.01	20	1230	30	<5	<20	26	0.13	<10	128	<10	6	141
251	L37N 7350E	10	0.2	2.22	30	100	<5	0.32	<1	20	46	57	4.79	<10	0.97	857	<1	0.01	35	860	36	<5	<20	26	0.14	<10	133	<10	11	175
252	L37N 7375E	10	0.4	2.26	15	150	<5	0.26	2	20	56	56	5.02	<10	0.98	981	4	<0.01	53	870	30	<5	<20	29	0.08	<10	100	<10	12	178
253	L37N 7400E	10	0.4	2.23	25	105	5	0.28	1	19	41	52	4.66	<10	0.82	897	3	<0.01	30	780	32	<5	<20	19	0.11	<10	114	<10	8	155
254	L37N 7425E	5	1.9	2.23	30	100	<5	0.75	4	21	33	91	4.33	<10	0.67	1300	3	0.01	39	1060	34	<5	<20	33	0.06	<10	79	<10	24	167
255	L37N 7450E	10	1.4	2.17	35	75	<5	0.81	3	18	33	72	4.57	<10	0.55	789	3	<0.01	25	640	36	<5	<20	32	0.08	<10	82	<10	21	131
256	L37N 7475E	5	1.1	2.33	40	85	<5	0.68	3	16	30	69	4.73	<10	0.43	621	4	0.01	28	570	36	<5	<20	31	0.10	<10	83	<10	16	138
257	L37N 7500E	10	0.4	1.63	25	105	<5	0.12	1	13	27	39	3.82	<10	0.51	359	3	<0.01	24	810	24	<5	<20	10	0.06	<10	74	<10	3	170
258	L37N 7525E	15	0.3	1.66	25	80	<5	0.23	1	20	35	54	4.42	<10	0.78	605	4	<0.01	34	890	24	<5	<20	17	0.07	<10	81	<10	5	169
259	L37N 7550E	5	0.7	1.52	10	75	<5	0.55	2	14	29	48	3.14	<10	0.53	911	2	0.01	31	600	24	<5	<20	24	0.06	<10	56	<10	14	157
260	L37N 7575E	5	0.2	1.64	10	110	<5	0.24	3	24	24	66	4.81	<10	0.52	1120	10	<0.01	50	1260	26	<5	<20	19	0.03	<10	69	<10	13	278
261	L37N 7600E	5	0.3	1.66	10	190	<5	0.21	4	21	27	67	4.92	<10	0.50	1064	13	<0.01	50	1370	28	<5	<20	16	0.02	<10	86	<10	8	369
262	L37N 7625E	5	0.7	1.76	15	155	<5	0.41	2	20	29	68	4.60	<10	0.61	957	8	<0.01	60	1310	36	<5	<20	19	0.03	<10	70	<10	9	233
263	L37N 7650E	5	1.1	2.26	15	150	<5	0.29	2	29	38	74	5.47	<10	0.75	1709	6	<0.01	47	790	36	<5	<20	19	0.09	<10	99	<10	7	250
264	L37N 7675E	5	1.1	2.40	15	105	<5	0.25	2	30	41	83	5.25	<10	0.77	1503	5	<0.01	55	950	38	<5	<20	16	0.08	<10	91	<10	10	274
265	L37N 7700E	5	0.3	2.15	10	120	<5	0.22	1	25	42	66	5.03	<10	0.85	1091	3	<0.01	43	680	32	<5	<20	15	0.10	<10	94	<10	5	192
266	L37N 7725E	5	1.2	1.88	10	155	<5	0.21	<1	23	35	53	4.94	<10	0.59	1768	4	0.01	26	1110	32	<5	<20	13	0.09	<10	89	<10	2	183
267	L37N 7750E	5	0.5	2.25	15	145	5	0.23	<1	26	51	79	6.03	<10	1.06	1404	4	<0.01	40	1000	32	<5	<20	16	0.10	<10	116	<10	<1	201
268	L37N 7775E	5	0.7	2.30	10	95	5	0.54	2	44	59	119	7.17	<10	1.28	1624	5	<0.01	60	930	36	<5	<20	24	0.09	<10	120	<10	10	228
269	L37N 7800E	15	0.3	2.24	5	120	<5	0.45	2	43	44	99	6.49	<10	1.13	1694	4	<0.01	52	1210	34	<5	<20	29	0.09	<10	107	<10	4	239
270	L38N 6900E	5	0.3	2.11	<5	105	<5	0.33	1	25	40	58	5.16	<10	0.95	1189	3	<0.01	39	870	32	<5	<20	30	0.12	<10	115	<10	6	177

23-Jun-05
ECO TECH LABORATORY LTD.

ICP CERTIFICATE OF ANALYSIS AK 2005-519

COLUMBIA YUKON EXPLORATIONS INC.

Et #	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
271	L38N 6925E	5	0.3	2.41	15	75	<5	0.30	<1	24	46	68	4.94	<10	0.94	690	2	0.01	40	910	34	<5	<20	25	0.14	<10	111	<10	8	153
272	L38N 6950E	5	1.4	2.13	<5	135	<5	0.23	1	21	49	72	5.17	<10	0.99	682	2	<0.01	45	730	30	<5	<20	19	0.12	<10	111	<10	5	181
273	L38N 6975E	5	<0.2	2.32	<5	130	<5	0.34	<1	21	56	61	5.09	<10	1.24	889	<1	0.02	30	730	32	<5	<20	38	0.15	<10	162	<10	5	141
274	L38N 7000E	5	0.5	2.61	15	120	5	0.28	<1	22	45	55	4.31	<10	0.97	1306	<1	0.01	27	890	36	<5	<20	43	0.12	<10	128	<10	6	123
275	L38N 7025E	5	0.4	2.32	20	140	<5	0.43	<1	16	33	48	3.84	<10	0.70	770	<1	0.02	22	1090	32	<5	<20	43	0.10	<10	113	<10	4	101
276	L38N 7050E	5	0.4	2.30	15	125	<5	0.34	<1	19	37	47	4.27	<10	0.83	1344	<1	0.01	23	790	32	<5	<20	33	0.11	<10	129	<10	5	119
277	L38N 7075E	5	0.2	2.48	25	95	<5	0.38	<1	20	39	50	4.39	<10	0.92	862	<1	0.01	22	830	32	<5	<20	35	0.13	<10	132	<10	7	114
278	L38N 7100E	5	0.3	2.47	25	100	<5	0.38	<1	20	42	61	4.34	<10	1.00	736	<1	0.01	28	670	32	<5	<20	38	0.16	<10	133	<10	9	106
279	L38N 7125E	5	0.5	2.55	25	100	<5	0.39	<1	20	44	64	4.38	<10	1.01	633	<1	0.01	29	840	36	<5	<20	43	0.16	<10	130	<10	7	105
280	L38N 7150E	5	0.3	2.53	20	130	<5	0.33	<1	20	51	57	4.63	<10	1.04	874	<1	0.01	34	750	36	<5	<20	36	0.16	<10	142	<10	8	134
281	L38N 7175E	5	0.2	2.45	5	130	<5	0.40	<1	19	45	48	5.09	<10	1.07	724	<1	0.02	23	830	32	<5	<20	36	0.18	<10	153	<10	7	131
282	L38N 7200E	5	0.3	2.25	15	90	<5	0.32	<1	23	43	63	4.97	<10	1.02	685	<1	0.02	27	770	32	<5	<20	29	0.15	<10	151	<10	8	123
283	L38N 7225E	5	0.3	2.07	5	95	<5	0.22	<1	16	45	49	4.81	<10	0.99	434	<1	0.01	26	550	30	<5	<20	23	0.19	<10	139	<10	6	107
284	L38N 7250E	10	0.4	2.77	30	95	<5	0.22	<1	17	56	100	4.97	<10	1.03	422	3	0.01	42	880	40	<5	<20	26	0.13	<10	143	<10	5	145
285	L38N 7275E	5	0.6	2.46	15	100	<5	0.39	2	21	46	66	4.62	<10	0.87	914	1	0.01	35	840	32	<5	<20	29	0.12	<10	115	<10	10	171
286	L38N 7300E	5	0.9	1.77	15	140	<5	0.12	3	18	25	58	4.74	<10	0.61	957	10	<0.01	45	890	30	<5	<							

291	L38N 7425E	5	0.8	1.72	20	95	<5	0.81	5	17	28	55	3.92	<10	0.55	1318	5	0.01	35	840	28	<5	<20	33	0.05	<10	62	<10	7	197
292	L38N 7450E	5	0.5	1.97	30	95	<5	0.69	3	18	38	59	4.42	<10	0.73	1080	4	<0.01	39	710	28	<5	<20	33	0.07	<10	90	<10	10	210
293	L38N 7475E	10	0.7	2.06	25	80	<5	0.68	4	18	40	73	4.60	<10	0.76	677	4	0.01	45	470	28	<5	<20	32	0.08	<10	89	<10	13	186
294	L38N 7500E	10	0.5	1.68	40	75	<5	0.24	1	11	35	47	4.33	<10	0.69	445	4	0.01	28	570	24	<5	<20	19	0.07	<10	92	<10	4	164
295	L38N 7525E	10	0.3	1.84	20	105	<5	0.21	<1	15	35	43	4.33	<10	0.62	649	3	<0.01	29	1460	26	<5	<20	15	0.08	<10	86	<10	4	167
296	L38N 7550E	5	0.6	1.72	20	85	<5	0.22	1	15	33	47	4.27	<10	0.72	694	2	<0.01	27	570	26	<5	<20	15	0.10	<10	84	<10	7	163
297	L38N 7575E	10	0.4	1.71	25	100	<5	0.21	<1	17	35	52	4.56	<10	0.77	750	4	<0.01	32	990	24	<5	<20	15	0.10	<10	89	<10	5	180
298	L38N 7600E	10	0.6	2.06	45	115	<5	0.18	<1	16	33	46	4.33	<10	0.65	618	3	<0.01	30	1210	28	<5	<20	14	0.09	<10	88	<10	3	169
299	L38N 7625E	10	0.5	1.82	40	115	5	0.22	<1	17	29	47	4.25	<10	0.63	791	5	0.01	31	1420	28	<5	<20	18	0.07	<10	80	<10	3	189
300	L38N 7650E	5	0.5	2.17	20	135	<5	0.26	1	23	32	55	4.61	<10	0.60	1109	3	<0.01	36	1610	32	<5	<20	17	0.08	<10	77	<10	5	197
301	L38N 7675E	5	0.7	2.53	20	95	<5	0.79	1	24	34	57	4.32	<10	0.60	1146	2	0.01	37	950	36	<5	<20	26	0.10	<10	76	<10	11	183
302	L38N 7700E	5	0.2	1.48	10	180	<5	0.44	2	21	30	49	4.84	<10	0.61	1708	4	<0.01	28	1100	44	<5	<20	21	0.09	<10	84	<10	1	162
303	L38N 7725E	5	0.4	1.96	20	95	<5	0.15	<1	17	52	42	4.09	<10	0.61	1040	4	<0.01	56	910	30	<5	<20	10	0.08	<10	68	<10	3	147
304	L38N 7750E	5	0.3	2.01	5	150	<5	0.29	1	36	52	83	5.40	<10	0.82	2063	3	<0.01	39	830	32	<5	<20	18	0.10	<10	103	<10	5	217

QC DATA:

Repeat:

1	L24N 6900E	15	0.3	2.40	15	95	<5	0.57	<1	18	49	50	4.12	<10	0.79	444	<1	0.02	35	890	32	5	<20	35	0.17	<10	125	<10	10	93
10	L24N 7125E	40	0.5	2.44	110	65	5	0.51	<1	21	42	25	4.64	<10	0.22	407	11	0.02	58	1170	34	20	<20	25	0.12	<10	67	<10	8	98
14	L24N 7225E	55																												
19	L24N 7350E	15	0.3	2.62	35	55	5	0.24	<1	14	22	49	4.71	<10	0.35	296	1	0.01	16	1160	36	<5	<20	17	0.13	<10	129	<10	5	95

Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
QC DATA:																														
Repeat:																														
25	L25N 6900E	405																												
28	L25N 6975E	5	0.6	2.57	110	100	<5	0.17	<1	15	39	41	4.99	<10	0.40	209	2	0.01	26	400	38	<5	<20	9	0.14	<10	110	<10	11	159
36	L25N 7200E	15	0.5	2.47	55	75	<5	0.80	1	15	19	39	4.26	<10	0.37	459	3	0.02	19	750	38	<5	<20	27	0.10	<10	82	<10	16	126
45	L25N 7425E	20	0.3	2.53	80	70	<5	0.33	<1	20	55	44	3.99	<10	0.47	354	<1	0.01	51	1080	40	<5	<20	22	0.14	<10	109	<10	12	116
54	L26N 7050E	10	0.2	1.19	35	90	<5	0.08	<1	8	18	19	3.64	<10	0.18	210	3	<0.01	13	960	28	<5	<20	5	0.07	<10	65	<10	2	129
64	L26N 7300E	65	0.5	2.70	270	155	<5	1.64	<1	20	70	60	4.29	<10	0.71	1905	<1	0.04	71	1010	40	<5	<20	43	0.10	<10	125	<10	16	148
66	L26N 7350E	130																												
71	L26N 7475E	5	0.7	3.15	60	110	<5	0.96	3	14	24	44	3.14	<10	0.50	2214	<1	0.02	23	920	36	<5	<20	34	0.10	<10	83	<10	13	148
73	L26N 7525E	250																												
80	L27N 7025E	<5	0.3	3.88	15	150	<5	0.45	1	23	65	102	4.78	<10	1.41	750	<1	0.05	46	560	34	<5	<20	35	0.18	<10	183	<10	9	135
89	L27N 7250E	<5	0.2	3.75	30	130	<5	0.39	<1	19	54	57	4.45	<10	1.06	440	<1	0.03	30	800	36	<5	<20	29	0.15	<10	159	<10	5	102
98	L27N 7475E	<5	0.3	3.34	25	135	<5	0.42	<1	20	54	76	5.06	<10	1.14	695	<1	0.03	27	1500	32	<5	<20	37	0.14	<10	178	<10	3	98
106	L27N 7675E	10	0.8	2.21	35	125	<5	0.06	<1	11	17	28	3.14	<10	0.31	814	2	0.01	15	990	30	<5	<20	2	0.07	<10	57	<10	3	121
108	L32N 7700E	115																												
115	L3350N 7550E	15	0.6	2.26	490	85	5	0.11	<1	17	30	33	4.12	<10	0.57	450	1	0.01	21	630	26	75	<20	8	0.11	<10	86	<10	<1	113
116	L3350N 7575E	80																												
124	L34N 6950E	55	0.3	2.30	105	105	<5	0.10	<1	10	14	22	2.83	<10	0.23	447	<1	0.02	8	970	28	<5	<20	11	0.10	<10	63	<10	<1	62
133	L34N 7175E	50	0.4	2.65	320	110	5	0.25	<1	14	17	31	3.81	<10	0.45	447	1	0.02	12	890	30	<5	<20	18	0.11	<10	84	<10	4	91
134	L34N 7200E	120																												
137	L34N 7275E	25																												
141	L34N 7375E	5	0.8	2.45	855	95	5	0.76	<1	20	33	76	4.17	20	0.77	1860	2	0.02	18	880	28	40	<20	43	0.09	<10	105	<10	46	108
150	L34N 7600E	10	0.8	1.93	265	165	5	0.20	<1	21	23	38	5.87	<10	0.69	1196	5	0.01	11	2340	30	90	<20	19	0.12	<10	141	<10	3	128
159	L35N 6900E	5	0.7	2.43	640	140	<5	0.66	<1	23	39	80	4.25	<10	0.69	1263	<1	0.02	28	820	32	<5	<20	36	0.15	<10	122	<10	28	162
168	L35N 7125E	5	1.1	2.36	805	115	<5	0.68	<1	20	29	70	4.97	<10	0.78	1117	2	0.02	18	1000	30	<5	<20	26	0.09	<10	137	<10	22	113
176	L35N 7325E	50	0.7	2.89	170	90	<5	0.30	<1	13	14	26	2.79	<10	0.30	645	<1	0.01	11	930	42	<5	<20	24	0.10	<10	56	<10	7	82
185	L35N 7550E	10	0.4	2.25	25	105	<5	0.24	2	15	31	37	4.02	<10	0.52	483	2	0.01	31	730	32	<5	<20	17	0.11	<10	78	<10	7	215
194	L35N 7775E	10	3.1	1.74	<5	220	10	0.40	4	19	20	89	8.11	<10	0.26	2140	16	0.01	36	2670	38	<5	<20	48	0.13	<10	134	<10	3	346
203	L36N 7075E	20	<0.2	2.15	80	85	<5	0.21	<1	20	35	49	4.15	<10	0.68	995	<1	0.02	29	520	28	<5	<20	20	0.13	<10	108	<10	8	135
209	L36N 7225E	80																												
211	L36N 7275E	25	0.2	2.60	130	110	<5	0.29	<1	16	23	39	3.66	<10	0.52	1050	<1	0.01	16	1170	34	<5	<20	22	0.10	<10	78	<10	7	93
220	L36N 7500E	5	0.6	2.27	30	130	<5	0.29	2	20	37	63	4.66	<10	0.69	888	8	<0.01	36	820	32	10	<20	20	0.08	<10	98	<10	10	198
229	L36N 7725E	5	0.8	2.09	25	125	<5	0.12	<1	16	25	38	3.80	<10	0.46	1080	2	<0.01	23	1070	36	<5	<20	15	0.09	<10	74	<10	5	166
238	L37N 7025E	5	<0.2	2.17	15	125	<5	0.36	<1	15	48	50	4.71	<10	1.07	824	<1	0.02	28	1150	30	<5	<20	27	0.13	<10	151	<10	8	135
246	L37N 7225E	5	0.4	2.69	15	65	<5	0.29	1	20	33	48	4.24	<10	0.78	656	<1	0.01	26	840	36	<5	<20	20	0.14	<10	104	<10	12	124
255	L37N 7450E	5	1.3	2.20	30	80	<5	0.79	4	18	33	72	4.58	<10	0.60	787	3	<0.01	26	620	34	<5	<20	33	0.09	<10	85	<10	20	134
264	L37N 7675E	15	<0.2	2.44	15	105	<5	0.27	3	30	42	81	5.39	<10	0.77	1438	4	0.01	57	930	38	<5	<20	18	0.09	<10	96	<10	10	292
273	L38N 6975E	<5	<0.2	2.47	<5	135	<5	0.39	<1	23	59	64	5.47	<10	1.33	957	<1	0.02	33	720	34	<5	<20	40	0.17	<10	171	<10	6	144
281	L38N 7175E	<5	0.3	2.35	10	120	5	0.39	<1	18	43	46	4.78	<10	1.02	683	<1	0.02	21	790	30	<5	<20	36	0.19	<10	145	<10	8	123
290	L38N 7400E	5	0.5	1.80	20	165	<5	0.21	2	16	29	48	4.14	<10	0.57	705	6	<0.01	38	930	28	<5	<20	14	0.06	<10	69	<10	5	205
299	L38N 7625E	15																												
GEO '05		130	1.4	1.12	60	165	<5	1.52	<1	19	60	84	4.07	<10	0.59	634	<1	0.02	32	710	24	<5	<20	54	0.10	<10	77	<10	9	76
GEO '05		145	1.6	1.13	60	165	<5	1.55	<1	19	60	84	4.03	<10	0.59	637	1	0.02	33	720	24	<5	<20	55	0.12	<10	77	<10	8	76
GEO '05		130	1.5	1.35	55	140	<5	1.21	<1	20	60	89	3.69	<10	0.72	540	<1	0.02	23	620	20	<5	<20	50	0.11	<1				

06-Jul-05

ECO TECH LABORATORY LTD.
10041 Dallas Drive
KAMLOOPS, B.C.
V2C 6T4

Phone: 250-573-5700
Fax : 250-573-4557

ICP CERTIFICATE OF ANALYSIS AK 2005-592

COLUMBIA YUKON EXPLORATIONS INC.
5936 Stafford Road
Nelson, BC
V1L 6P3

ATTENTION: Bernie Augsten / Gillian Feyer

No. of samples received: 265

Sample type: Soil

Project : Barnes Creek

Shipment #: n/a

Samples submitted by: Bernhardt Augsten

Values in ppm unless otherwise reported

Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
1	L26N 6100E	30	0.2	2.77	60	90	<5	0.24	<1	20	38	61	4.14	<10	0.47	488	<1	0.02	33	1560	4	<5	<20	29	0.12	<10	122	<10	6	83
2	L26N 6125E	100	1.0	3.13	145	70	<5	0.20	<1	18	37	55	3.91	<10	0.49	243	<1	0.02	31	820	8	<5	<20	18	0.14	<10	108	<10	7	89
3	L26N 6150E	10	0.3	1.89	20	85	<5	0.18	<1	12	14	39	3.78	<10	0.32	494	2	0.01	9	2460	6	<5	<20	20	0.10	<10	93	<10	4	59
4	L26N 6175E	10	0.4	1.76	20	120	<5	0.29	<1	12	18	37	3.52	<10	0.37	550	<1	0.02	11	1830	18	<5	<20	24	0.09	<10	91	<10	4	63
5	L26N 6200E	10	0.6	2.67	15	90	<5	0.20	<1	14	20	54	3.60	<10	0.38	548	<1	0.02	12	2040	6	<5	<20	27	0.08	<10	96	<10	3	69
6	L26N 6225E	10	0.4	2.47	10	125	<5	0.14	<1	15	17	49	4.02	<10	0.31	1305	<1	0.02	13	1140	10	<5	<20	23	0.11	<10	103	<10	2	74
7	L26N 6250E	5	1.5	3.02	20	115	<5	0.13	<1	13	24	38	3.57	<10	0.44	833	<1	0.02	20	1110	10	<5	<20	14	0.12	<10	100	<10	8	74
8	L26N 6275E	5	0.3	2.83	15	115	<5	0.12	<1	15	20	46	3.53	<10	0.45	426	<1	0.02	15	920	8	<5	<20	15	0.13	<10	99	<10	6	79
9	L26N 6300E	5	0.3	2.40	25	60	<5	0.29	<1	7	11	41	2.86	<10	0.14	89	<1	0.02	8	680	8	<5	<20	23	0.11	<10	61	<10	9	33
10	L26N 6325E	5	0.4	4.37	45	90	<5	0.10	<1	17	18	80	4.08	<10	0.38	200	<1	0.02	18	730	6	<5	<20	15	0.17	<10	95	<10	18	75
11	L26N 6350E	10	0.6	2.64	20	105	<5	0.13	<1	14	15	30	3.09	<10	0.45	474	<1	0.02	14	690	12	<5	<20	19	0.12	<10	80	<10	5	69
12	L26N 6375E	10	0.3	3.05	25	110	<5	0.13	<1	19	18	129	4.45	<10	0.55	316	2	0.02	27	970	6	<5	<20	18	0.11	<10	110	<10	6	82
13	L26N 6400E	20	0.3	2.98	35	80	<5	0.18	<1	16	19	118	3.93	<10	0.64	349	<1	0.02	22	1070	8	<5	<20	20	0.11	<10	99	<10	8	91
14	L26N 6425E	15	1.0	2.18	180	105	<5	1.67	<1	16	26	240	3.38	<10	0.48	2659	3	0.02	48	1280	6	<5	<20	54	0.05	<10	91	<10	20	62
15	L26N 6450E	20	0.2	1.79	80	75	<5	0.19	<1	11	16	28	4.18	<10	0.42	540	2	0.01	9	1940	14	<5	<20	14	0.10	<10	106	<10	1	61
16	L26N 6475E	20	0.4	2.85	55	80	<5	0.32	<1	18	27	59	4.47	<10	0.61	392	1	0.02	20	1610	4	<5	<20	28	0.12	<10	120	<10	7	77
17	L26N 6500E	30	1.0	2.84	110	85	<5	0.72	<1	20	27	88	4.86	<10	0.71	656	<1	0.02	24	1200	8	<5	<20	34	0.14	<10	129	<10	15	81
18	L26N 6525E	10	0.4	2.75	40	75	<5	0.10	<1	14	33	39	3.76	<10	0.44	323	<1	0.02	18	980	10	<5	<20	12	0.13	<10	110	<10	7	75
19	L26N 6550E	10	0.3	2.36	60	75	<5	0.18	<1	17	23	55	4.36	<10	0.55	550	2	0.01	18	2030	8	<5	<20	19	0.09	<10	97	<10	3	80
20	L26N 6575E	15	0.5	2.06	115	65	<5	0.21	<1	16	25	64	4.63	<10	0.64	355	2	0.01	18	960	8	<5	<20	21	0.08	<10	112	<10	6	76
21	L26N 6600E	10	0.5	1.85	25	90	<5	0.15	<1	10	22	51	4.87	<10	0.34	171	2	0.02	15	1150	10	<5	<20	18	0.11	<10	110	<10	<1	49
22	L26N 6625E	5	0.2	2.93	30	105	<5	0.12	<1	16	17	48	3.90	<10	0.33	734	1	0.01	16	1860	10	<5	<20	14	0.11	<10	80	<10	6	55
23	L26N 6650E	5	<0.2	2.91	20	80	<5	0.17	<1	17	26	56	3.87	<10	0.42	477	<1	0.02	22	1170	10	<5	<20	20	0.13	<10	115	<10	7	68
24	L26N 6675E	10	0.2	3.35	35	65	<5	0.18	<1	17	26	49	4.06	<10	0.44	221	<1	0.02	23	700	8	<5	<20	17	0.13	<10	107	<10	12	58
25	L26N 6700E	5	0.3	3.43	35	100	<5	0.12	<1	14	27	41	3.49	<10	0.47	581	<1	0.02	20	1250	6	<5	<20	15	0.11	<10	94	<10	6	81
26	L26N 6725E	10	0.6	3.23	30	120	<5	0.11	<1	16	33	38	3.86	<10	0.55	384	<1	0.02	23	1050	8	<5	<20	13	0.13	<10	103	<10	9	111
27	L26N 6750E	5	0.7	3.49	25	105	<5	0.16	<1	18	27	51	3.59	<10	0.51	1010	<1	0.03	23	1080	8	<5	<20	20	0.14	<10	103	<10	12	101
28	L26N 6775E	10	0.2	2.95	20	110	<5	0.42	<1	22	28	61	4.28	<10	0.55	1215	<1	0.02	41	1610	8	<5	<20	37	0.09	<10	103	<10	7	89
29	L26N 6800E	10	0.7	3.01	50	120	<5	0.75	1	18	38	74	4.23	<10	0.80	1276	<1	0.03	31	1070	8	<5	<20	39	0.11	<10	121	<10	15	155
30	L26N 6825E	10	0.4	2.76	35	105	<5	0.18	<1	14	26	29	2.90	<10	0.27	1378	<1	0.02	25	1740	14	<5	<20	18	0.10	<10	68	<10	5	64

ECO TECH LABORATORY LTD.

ICP CERTIFICATE OF ANALYSIS AK 2005-592

COLUMBIA YUKON EXPLORATIONS INC.

Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn	
31	L26N 6850E	10	0.4	3.21	25	90	<5	0.19	<1	16	29	48	3.96	<10	0.73	473	<1	0.03	25	1140	8	5	<20	26	0.13	<10	119	<10	7	84	
32	L26N 6875E	10	0.7	3.07	30	110	<5	0.08	<1	11	17	17	3.27	<10	0.26	630	1	0.02	18	880	16	<5	<20	10	0.09	<10	58	<10	6	120	
33	L27N 5950E	15	0.4	2.88	50	120	<5	0.74	<1	15	39	74	3.71	<10	0.80	992	<1	0.03	36	920	12	<5	<20	34	0.12	<10	114	<10	13	120	
34	L27N 5975E	20	0.4	2.95	30	100	<5	0.56	<1	16	39	69	3.78	<10	0.85	588	<1	0.04	31	1020	10	<5	<20	38	0.10	<10	116	<10	9	100	
35	L27N 6000E	5	0.2	2.88	15	70	<5	0.18	<1	15	25	39	3.03	<10	0.44	366	<1	0.02	19	1370	8	<5	<20	20	0.09	<10	91	<10	6	70	
36	L27N 6025E	5	<0.2	2.69	15	55	<5	0.09	<1	8	12	18	2.66	<10	0.21	294	<1	0.02	8	1340	10	<5	<20	11	0.09	<10	60	<10	6	64	
37	L27N 6050E	25	<0.2	2.86	35	75	<5	0.24	<1	21	34	85	4.04	<10	0.64	554	2	0.02	46	1210	4	<5	<20	26	0.09	<10	103	<10	6	118	
38	L27N 6075E	45	0.2	2.56	30	75	<5	0.15	<1	17	24	48	3.53	<10	0.35	498	1	0.02	22	1430	8	<5	<20	10	0.10	<10	89	<10	4	80	
39	L27N 6100E	10	<0.2	2.59	15	150	<5	0.49	<1	23	41	54	4.53	<10	0.84	2171	2	0.04	30	1790	14	<5	<20	31	0.10	<10	141	<10	3	134	
40	L27N 6125E	10	0.2	2.80	15	75	<5	0.19	<1	18	33	53	3.78	<10	0.57	880	<1	0.02	26	1220	4	<5	<20	14	0.09	<10	107	<10	5	103	
41	L27N 6150E	10	0.2	2.13	15	150	<5	0.21	<1	15	24	42	3.12	<10	0.42	1536	<1	0.02	19	1020	16	<5	<20	16	0.09	<10	85	<10	5	79	
42	L27N 6175E	10	<0.2	2.28	15	95	<5	0.17	<1	11	14	53	3.05	<10	0.44	751	<1	0.02	11	1700	8	<5	<20	12	0.08	<10	92	<10	3	74	
43	L27N 6200E	10	0.2	3.37	20	145	<5	0.19	<1	16	26	64	3.65	<10	0.70	596	<1	0.02	24	880	6	<5	<20	16	0.13	<10	114	<10	10	101	
44	L27N 6225E	10	0.3	2.95	20	150	<5	0.20	<1	16	32	66	3.73	<10	0.79	427	2	0.03	28	840	2	<5	<20	24	0.13	<10	115	<10	9	103	
45	L27N 6250E	5	0.2	1.82	10	125	<5	0.42	<1	17	54	43	3.50	<10	0.77	1421	1	0.06	39	1060	<2	<5	<20	48	0.08	<10	100	<10	10	71	
46	L27N 6275E	5	0.4	3.05	15	100	<5	0.11	<1	11	16	41	2.84	<10	0.47	344	<1	0.02	12	650	6	<5	<20	12	0.11	<10	85	<10	6	68	
47	L27N 6300E	5	0.2	2.90	20	155	<5	0.17	<1	15	31	46	3.17	<10	0.61	756	<1	0.02	24	880	6	<5	<20	18	0.10	<10	93	<10	6	88	
48	L27N 6325E	<5	0.2	2.41	15	170	<5	0.49	<1	12	34	28	2.91	<10	0.58	1560	<1	0.03	26	1000	6	<5	<20	27	0.09	<10	82	<10	4	71	
49	L27N 6350E	5	0.2	2.65	30	85	<5	0.55	<1	14	54	36	3.11	<10	0.54	454	<1	0.03	41	420	6	<5	<20	25	0.12	<10	81	<10	10	79	
50	L27N 6375E	10	<0.2	4.79	35	150	<5	0.59	<1	26	43	81	5.53	<10	2.03	1031	<1	0.08	39	410	2	<5	<20	51	0.17	<10	184	<10	10	97	
51	L27N 6400E	5	0.2	2.86	25	115	<5	0.21	<1	20	73	52	4.17	<10	0.67	596	2	0.02	108	1260	12	<5	<20	22	0.11	<10	95	<10	13	86	
52	L27N 6425E	5	0.2	2.96	25	120	<5	0.23	<1	18	46	65	4.08	<10	0.83	700	1	0.02	43	1580	6	<5	<20	16	0.10	<10	118	<10	6	98	
53	L27N 6450E	5	0.2	3.12	30	165	<5	0.20	<1	20	24	62	3.98	<10	0.43	467	<1	0.02	32	970	6	<5	<20	21	0.09	<10	83	<10	6	73	
54	L27N 6475E	10	0.3	2.52	15	65	<5	0.25	<1	27	26	149	5.29	<10	0.85	490	4	0.02	39	1100	<2	<5	<20	26	0.05	<10	108	<10	<1	80	
55	L27N 6500E	5	0.3	2.37	15	85	10	0.12	<1	19	23	47	3.81	<10	0.35	916	<1	0.02	24	930	10	<5	<20	11	0.09	<10	84	<10	2	85	
56	L27N 6525E	5	0.3	2.28	20	80	<5	0.18	<1	16	24	52	3.53	<10	0.43	768	1	0.02	29	1150	10	<5	<20	14	0.07	<10	79	<10	2	68	
57	L27N 6550E	5	0.2	2.33	15	85	<5	0.21	<1	13	23	41	2.81	<10	0.29	1019	1	0.02	23	1150	10	<5	<20	16	0.07	<10	73	<10	3	83	
58	L27N 6575E	15	<0.2	2.48	60	70	<5	0.32	<1	16	36	56	3.83	<10	0.54	360	<1	0.02	28	1300	4	<5	<20	20	0.09	<10	105	<10	3	110	
59	L27N 6600E	10	<0.2	3.07	30	75	<5	0.24	<1	18	34	69	4.45	<10	0.52	407	<1	0.02	29	1120	12	<5	<20	16	0.10	<10	113	<10	20	5	105
60	L27N 6625E	10	0.3	3.49	35	110	<5	0.24	<1	23	51	89	4.60	<10	1.04	639	<1	0.03	42	890	6	<5	<20	24	0.13	<10	149	<10	7	109	
61	L27N 6650E	5	0.2	2.84	20	110	<5	0.36	<1	22	44	70	4.10	<10	0.79	1210	1	0.04	44	1160	2	<5	<20	35	0.09	<10	120	<10	6	104	
62	L27N 6675E	10	0.2	3.00	20	140	<5	0.23	<1	18	38	57	3.96	<10	0.83	1131	<1	0.03	28	1070	8	<5	<20	20	0.12	<10	129	<10	6	102	
63	L27N 6700E	5	<0.2	2.98	20	105	<5	0.18	<1	16	25	56	3.13	<10	0.52	736	<1	0.02	25	1050	6	<5	<20	17	0.09	<10	91	<10	5	73	
64	L27N 6725E	5	0.2	2.41	30	90	<5	0.23	<1	9	10	26	2.77	<10	0.18	186	<1	0.02	8	540	6	<5	<20	12	0.10	<10	69	<10	3	45	
65	L27N 6750E	5	<0.2	2.93	15	90	<5	0.18	<1	19	42	56	3.71	<10	0.69	382	<1	0.03	31	850	6	<5	<20	13	0.13	<10	114	<10	6	77	
66	L27N 6775E	5	<0.2	2.97	15	85	<5	0.14	<1	15	15	59	3.41	<10	0.58	456	<1	0.03	13	880	4	<5	<20	14	0.15	<10	104	<10	8	76	
67	L27N 6800E	5	0.2	2.17	10	135	<5	0.45	<1	19	31	94	3.98	<10	0.99	1363	<1	0.05	18	660	4	10	<20	52	0.11	<10	139	<10	4	95	
68	L27N 6825E	10	0.4	2.85	30	115	<5	0.37	<1	20	36	85	4.25	<10	0.91	1267	2	0.02	23	1950	4	10	<20	42	0.08	<10	133	<10	2	104	
69	L27N 6850E	5	0.2	3.43	25	195	<5	0.23	<1	21	76	69	4.78	<10	1.34	922	<1	0.05	41	770	2	10	<20	26	0.18	<10	170	<10	8	93	
70	L27N 6875E	10	<0.2	3.95	65	160	<5	0.20	<1	16	34	59	3.60	<10	0.82	414	<1	0.03	30	710	6	<5	<20	23	0.15	<10	120	<10	12	86	

ECO TECH LABORATORY LTD.

ICP CERTIFICATE OF ANALYSIS AK 2005-592

COLUMBIA YUKON EXPLORATIONS INC.

Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
71	L28N 5900E	5	0.4	2.82	20	140	<5	0.23	<1	15	38	49	4.02	<10	0.67	838	1	0.03	21	1180	8	<5	<20	19	0.11	<10	143	<10	6	101
72	L28N 5925E	20	0.4	2.81	30	245	<5	0.36	<1	19	52	89	4.45	<10	1.20	802	1	0.04	37	1430	6	5	<20	47	0.12	<10	162	<10	11	111
73	L28N 5975E	15	0.4	3.25	35	150	<5	0.43	<1	18	43	62	4.35	<10	1.06	746	<1	0.04	30	780	4	<5	<20	25	0.13	<10	146	<10	11	116
74	L28N 6000E	10	0.5	2.30	45	100	<5	0.91	1	12	34	75	2.96	<10	0.71	1023	2	0.05	28	730	2	<5	<20	38	0.06	<10	102	<10	10	90
75	L28N 6025E	20	0.4	2.66	35	155	<5	0.79	1	18	48	106	4.30	<10	1.20	1258	<1	0.05	38	710	2	<5	<20	38	0.11	<10	152	<10	16	134
76	L28N 6050E	40	0.3	3.06	50	165	<5	0.36	<1	20	45	76	4.70	<10	1.21	932	<1	0.05	31	750	6	<5	<20	24	0.13	<10	167	<10	11	114
77	L28N 6075E	15	0.4	2.97	25	160	<5	0.29	1	16	39	54	4.33	<10	1.08	888	<1	0.04	24	1940	6	<5	<20	20	0.11	<10	153	<10	5	112
78	L28N 6100E	15	0.5	3.02	30	190	<5	0.19	<1	15	39	52	3.94	<10	0.86	900	<1	0.03	24	1170	8	<5	<20	17	0.12	<10	132	<10	8	109
79	L28N 6125E	10	0.3	2.89	15	185	<5	0.23	<1	18	58	58	4.70	<10	1.03	547	<1	0.04	29	740	8	<5	<20	22	0.17	<10	166	<10	9	106
80	L28N 6150E	20	0.3	2.34	15	130	<5	0.28	<1	16	21	63	3.86	<10	0.67	1124	<1	0.02	18	1390	6	<5	<20	23	0.10	<10	109	<10	2	104
81	L28N 6175E	5	0.2	2.72	25	135	<5	0.22	<1	15	31	47	3.58	<10	0.77	462	<1	0.02	19	710	4	<5	<20	18	0.13	<10	111	<10	4	68
82	L28N 6200E	5	0.3	2.04	20	100	<5	0.20	<1	10	18	29	2.85	<10	0.41	748	<1	0.02	11	1660	10	<5	<20	17	0.09	<10	83	<10	3	69
83	L28N 6225E	10	0.2	2.16	15	95	<5	0.11	<1	8	19	30	2.55	<10	0.45	353	<1	0.01	11	1050	2	<5	<20	10	0.09	<10	75	<10	4	68
84	L28N 6250E	5	0.2	3.03	20	285	<5	0.34	<1	17	35	50	3.83	<10	1.19	481	<1	0.03	27	340	2	<5	<20	34	0.15	<10	122	<10	7	84
85	L28N 6275E	5	0.2	3.12	20	195	<5	0.31	<1	23	32	59	4.26	<10	1.40	1260	<1	0.04	28	780	4	<5	<20	32	0.15	<10	135	<10	6	124
86	L28N 6300E	5 <0.2	3.93	10	250	5	0.24	<1	22	33	25	4.71	<10	1.43	621	<1	0.05	20	490	4	<5	<20	28	0.20	<10	137	<10	8	142	
87	L28N 6325E	5	0.4	2.74	25	130	<5	0.58	<1	19	23	46	4.38	<10	1.49	549	<1	0.04	22	360	2	<5	<20	41	0.13	<10	133	<10	7	115
88	L28N 6350E	5	0.2	1.91	25	85	<5	0.10	<1	13	25	30	3.24	<10	0.26	680	<1	0.02	13	910	14	<5	<20	7	0.12	<10	84	<10	4	60
89	L28N 6375E	10	0.2	2.51	25	135	<5	0.16	<1	18	26	51	3.84	<10	0.82	726	<1	0.02	19	570	4	<5	<20	11	0.13	<10	124	<10	5	90
90	L28N 6400E	10	0.3	2.57	25	100	<5	0.11	<1	13	27	50	3.11	<10	0.56	488	<1	0.02	17	750	6	<5	<20	14	0.11	<10	101	<10	4	67
91	L28N 6425E	20	0.2	2.90	30	185	<5	0.14	<1	17	29	54	4.19	<10	0.75	1234	<1	0.02	21	2230	6	<5	<20	15	0.12	<10	135	<10	3	107
92	L28N 6450E	10	0.5	2.91	20	130	<5	0.10	<1	14	33	31	3.24	<10	0.40	578	1	0.02	25	800	6	<5	<20	10	0.09	<10	86	<10	5	90
93	L28N 6500E	15 <0.2	2.86	25	150	<5	0.30	<1	20	44	78	3.67	<10	0.94	342	<1	0.03	30	540	4	<5	<20	26	0.12	<10	126	<10	13	82	
94	L28N 6550E	40	0.4	3.00	45	130	<5	0.14	<1	16	35	52	4.02	<10	0.78	553	<1	0.02	24	460	6	<5	<20	14	0.12	<10	128	<10	7	109
95	L28N 6575E	10	0.3	2.84	20	185	<5	0.31	<1	21	40	67	5.29	<10	1.12	683	2	0.03	29	1260	6	<5	<20	27	0.13	<10	171	<10	5	113
96	L28N 6600E	5	0.2	3.25	20	130	<5	0.15	<1	15	52	49	4.16	<10	0.91	429	<1	0.03	25	720	8	<5	<20	14	0.16	<10	155	<10	8	88
97	L28N 6625E	5	0.6	3.19	25	115	<5	0.70	1	16	54	56	4.08	<10	0.97	1115	<1	0.04	30	620	6	<5	<20	31	0.15	<10	144	<10	16	105
98	L28N 6650E	5	0.2	2.81	20	145	<5	0.17	<1	18	53	50	4.57	<10	0.95	507	<1	0.03	28	530	8	<5	<20	15	0.15	<10	155	<10	6	102
99	L28N 6675E	5	0.4	3.35	20	90	<5	0.10	<1	9	27	35	3.12	<10	0.45	212	<1	0.02	21	1680	6	<5	<20	8	0.09	<10	78	<10	3	87
100	L28N 6700E	5	0.2	2.49	15	320	<5	0.28	1	17	33	49	4.04	<10	0.81	1306	<1	0.03	22	1040	6	<5	<20	21	0.13	<10	126	<10	4	138
101	L28N 6725E	5	0.2	2.82	15	140	<5	0.15	<1	17	44	59	4.02	<10	0.80	824	2	0.02	30	870	8	<5	<20	13	0.11	<10	125	<10	4	113
102	L28N 6750E	10	0.2	2.86	15	235	<5	0.51	3	35	56	116	5.86	<10	1.45	1959	4	0.04	52	1140	6	<5	<20	43	0.09	<10	188	<10	5	205
103	L28N 6775E	10	0.2	3.36	50	115	<5	0.27	2	23	36	74	4.90	<10	0.94	749	2	0.03	36	1250	4	<5	<20	40	0.11	<10	143	<10	6	190
104	L28N 6800E	5	0.2	3.14	35	80	<5	0.17	<1	17	28	29	4.22	<10	0.67	349	<1	0.03	20	530	6	<5	<20	14	0.18	<10	128	<10	8	96
105	L28N 6825E	5 <0.2	2.59	15	90	<5	0.21	<1	15	20	25	3.26	<10	0.55	466	<1	0.02	11	690	6	<5	<20	16	0.16	<10	83	<10	9	65	

ECO TECH LABORATORY LTD.

ICP CERTIFICATE OF ANALYSIS AK 2005-592

COLUMBIA YUKON EXPLORATIONS INC.

Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
106	L28N 6850E	5 <0.2	3.19	25	95	<5	0.15	<1	15	19	18	3.69	<10	0.44	416	<1	0.02	10	670	8	<5	<20	10	0.19	<10	89	<10	10	83	
107	L28N 6875E	10 0.2	2.03	15	75	<5	0.11	<1	10	17	14	2.89	<10	0.22	258	<1	0.02	9	960	10	<5	<20	8	0.15	<10	73	<10	5	58	
108	L29N 5900E	15 0.4	3.65	40	135	<5	0.73	<1	18	42	97	4.23	<10	1.01	979	<1	0.05	32	810	6	<5	<20	38	0.15	<10	139	<10	19	112	
109	L29N 5925E	15 0.2	3.56	45	180	<5	0.61	<1	21	51	85	5.01	<10	1.20	737	<1	0.05	34	920	6	<5	<20	42	0.16	<10	170	<10	13	115	
110	L29N 5950E	25 0.4	2.52	30	155	<5	0.83	1	18	48	90	4.10	<10	1.20	1180	<1	0.06	34	820	<2	<5	<20	44	0.10	<10	141	<10	19	96	
111	L29N 5975E	20 0.3	2.43	30	125	<5	0.40	<1	16	38	63	3.87	<10	0.91	675	<1	0.03	26	730	6	<5	<20	26	0.12	<10	128	<10	8	101	
112	L29N 6000E	20 0.5	3.16	45	170	<5	0.78	<1	21	72	117	5.01	<10	1.43	1064	<1	0.10	43	730	6	<5	<20	54	0.12	<10	164	<10	16	97	
113	L29N 6025E	10 0.3	3.35	20	175	<5	0.23	<1	19	48	54	4.63	<10	1.07	640	<1	0.03	27	1340	6	<5	<20	30	0.13	<10	159	<10	8	135	
114	L29N 6050E	55 0.3	2.46	45	75	<5	0.26	<1	10	29	40	3.45	<10	0.73	375	<1	0.02	17	520	8	<5	<20	19	0.10	<10	97	<10	7	68	
115	L29N 6075E	30 <0.2	2.96	45	95	<5	0.29	<1	15	34	24	3.59	<10	0.68	528	<1	0.03	16	1290	8	<5	<20	16	0.12	<10	108	<10	8	121	
116	L29N 6100E	20 0.5	2.48	40	130	<5	0.25	<1	16	31	58	3.67	<10	0.78	1453	2	0.03	22	1020	2	5	<20	15	0.10	<10	125	<10	5	105	
117	L29N 6125E	35 0.2	2.85	45	260	<5	0.27	<1	18	42	56	4.59	<10	1.02	907	<1	0.03	28	1180	6	<5	<20	29	0.14	<10	154	<10	5	127	
118	L29N 6150E	25 0.3	3.25	40	215	<5	0.40	1	29	61	104	5.28	<10	1.26	917	<1	0.04	46	1270	4	<5	<20	49	0.14	<10	179	<10	8	194	
119	L29N 6175E	5 0.6	2.57	25	130	<5	0.81	2	15	43	62	3.79	<10	0.97	1603	1	0.03	27	760	4	<5	<20	37	0.09	<10	133	<10	12	174	
120	L29N 6200E	10 0.5	1.90	10	135	<5	0.17	<1	12	8	67	3.26	<10	0.30	871	2	0.01	8	2870	6	<5	<20	10	0.07	<10	68	<10	2	56	
121	L29N 6225E	5 0.3	2.03	15	75	<5	0.08	<1	7	19	27	2.73	<10	0.34	247	<1	0.01	11	980	8	<5	<20	7	0.09	<10	73	<10	3	52	
122	L29N 6250E	5 0.2	2.23	10	45	<5	0.06	<1	11	11	21	2.85	<10	0.64	712	2	0.01	9	1150	6	10	<20	2	0.09	<10	76	<10	3	42	
123	L29N 6275E	10 0.3	2.32	15	185	<5	0.45	<1	18	17	143	4.60	<10	0.58	2303	<1	0.02	13	3130	<2	<5	<20	57	0.10	<10	116	<10	4	89	
124	L29N 6300E	10 0.2	1.29	10	110	<5	0.17	<1	11	10	46	2.73	<10	0.24	817	<1	0.01	9	1340	10	<5	<20	13	0.08	<10	62	<10	2	58	
125	L29N 6325E	5 <0.2	2.31	15	80	<5	0.20	<1	16	93	31	3.96	<10	1.07	325	<1	0.02	38	450	2	<5	<20	12	0.15	<10	137	<10	11	92	
126	L29N 6350E	15 0.2	2.65	25	65	<5	0.16	<1	11	24	29	3.39	<10	0.48	222	<1	0.02	11	350	6	<5	<20	14	0.13	<10	104	<10	11	54	
127	L29N 6375E	5 <0.2	2.31	15	100	<5	0.18	<1	14	41	59	4.86	<10	0.86	419	<1	0.02	21	950	12	<5	<20	28	0.16	<10	170	<10	4	77	
128	L29N 6400E	5 0.3	4.11	20	95	<5	0.07	<1	12	18	33	2.72	<10	0.30	623	<1	0.03	13	1650	<2	5	<20	11	0.12	<10	77	<10	10	55	
129	L29N 6425E	5 <0.2	2.87	20	165	<5	0.23	<1	18	47	52	3.85	<10	1.09	837	<1	0.03	22	1060	8	<5	<20	20	0.15	<10	142	<10	8	92	
130	L29N 6450E	5 0.3	1.49	10	110	<5	0.08	1	10	18	25	3.14	<10	0.43	623	<1	0.02	11	370	8	<5	<20	11	0.10	<10	90	<10	4	56	
131	L29N 6475E	5 0.3	1.87	10	165	<5	0.20	<1	12	24	18	3.57	<10	0.69	1020	<1	0.02	12	520	10	<5	<20	18	0.12	<10	110	<10	5	75	
132	L29N 6500E	5 0.2	2.97	15	105	<5	0.46	1	18	41	61	4.07	<10	0.97	460	<1	0.04	28	470	4	<5	<20	33	0.12	<10	133	<10	10	107	
133	L29N 6525E	5 0.3	3.63	20	135	<5	0.43	<1	21	47	67	4.64	<10	0.98	716	<1	0.04	30	550	8	<5	<20	24	0.17	<10	156	<10	15	125	
134	L29N 6550E	5 <0.2	2.66	15	210	<5	0.23	<1	17	44	44	4.56	<10	1.10	1909	<1	0.04	21	500	6	<5	<20	22	0.18	<10	164	<10	8	102	
135	L29N 6575E	5 <0.2	3.14	15	150	<5	0.26	<1	18	44	55	4.25	<10	0.93	776	<1	0.03	25	970	8	<5	<20	25	0.15	<10	144	<10	7	119	
136	L29N 6600E	5 0.2	2.72	10	115	<5	0.17	<1	14	38	36	4.35	<10	0.80	630	<1	0.02	19	750	8	<5	<20	14	0.19	<10	155	<10	8	96	
137	L29N 6625E	10 0.2	1.72	5	90	<5	0.09	<1	11	16	29	3.69	<10	0.45	586	<1	0.02	10	760	14	<5	<20	13	0.14	<10	110	<10	5	63	
138	L29N 6650E	10 <0.2	2.79	30	140	<5	0.22	<1	19	45	61	4.96	<10	1.10	780	2	0.02	23	1870	8	<5	<20	22	0.11	<10	161	<10	4	123	
139	L29N 6675E	5 <0.2	2.73	20	155	<5	0.18	<1	14	39	45	4.14	<10	0.87	568	<1	0.03	24	630	8	<5	<20	14	0.11	<10	140	<10	5	105	
140	L29N 6700E	5 0.2	3.43	5	210	<5	0.20	1	16	39	48	4.61	<10	1.07	1173	<1	0.03	21	1020	<2	<5	<20	20	0.15	<10	175	<10	8	99	
141	L29N 6725E	<5 0.2	3.81	20	135	<5	0.17	<1	14	19	34	3.46	<10	0.68	580	<1	0.02	12	1490	8	<5	<20	15	0.12	<10	102	<10	6	77	
142	L29N 6750E	5 0.2	3.08	25	200	<5	0.33	<1	22	43	68	5.39	<10	1.27	887	<1	0.03	30	780	16	<5	<20	24	0.15	<10	182	<10	7	141	
143	L29N 6775E	<5 0.2	2.57	10	160	<5	0.14	<1	16	35	40	4.01	<10	0.81	1406	<1	0.02	23	920	8	<5	<20	17	0.12	<10	126	<10	3	123	
144	L29N 6800E	5 0.2	2.46	15	110	<5	0.12	<1	13	31	31	3.55	<10	0.65	308	<1	0.02	18	660	10	<5	<20	10	0.14	<10	116	<10	4	80	
145	L29N 6825E	10 0.3	3.45	30	285	<5	0.37	<1	25	72	161	5.50	<10	1.81	598	<1	0.04	54	970	4	15	<20	25	0.15	<10	210	<10	9	121	

06-Jul-05

ECO TECH LABORATORY LTD.

ICP CERTIFICATE OF ANALYSIS AK 2005-592

COLUMBIA YUKON EXPLORATIONS INC.

Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
146	L29N 6850E	10	0.2	3.25	15	155	<5	0.19	<1	17	45	53	4.46	<10	1.08	669	<1	0.03	25	980	6	<5	<20	14	0.12	<10	151	<10	5	116
147	L29N 6875E	10	0.3	3.29	25	200	<5	0.29	<1	18	39	64	4.45	<10	1.09	1097	<1	0.04	27	1310	8	<5	<20	24	0.12	<10	150	<10	9	126
148	L30N 5900E	5	<0.2	3.10	20	95	<5	0.14	<1	12	28	42	3.54	<10	0.63	552	<1	0.02	16	2080	10	<5	<20	28	0.12	<10	107	<10	5	105
149	L30N 5925E	5	0.3	2.91	50	110	<5	0.11	<1	12	23	30	3.00	<10	0.41	640	<1	0.02	14	1570	12	<5	<20	11	0.11	<10	80	<10	5	93
150	L30N 5950E	5	0.4	2.85	35	110	<5	0.13	<1	14	30	56	3.06	<10	0.57	462	3	0.02	17	880	10	<5	<20	16	0.09	<10	92	<10	7	60
151	L30N 5975E	45	0.3	3.54	40	170	<5	0.12	<1	18	30	61	3.73	<10	0.64	490	4	0.02	22	1180	12	10	<20	14	0.11	<10	112	<10	6	90
152	L30N 6000E	10	0.2	2.85	25	230	<5	0.44	2	17	43	56	4.35	<10	1.14	1278	5	0.03	39	1000	12	20	<20	30	0.10	<10	136	<10	9	114
153	L30N 6025E	10	<0.2	1.94	15	100	<5	0.28	<1	16	25	23	3.46	<10	0.75	1022	<1	0.02	14	310	8	<5	<20	21	0.12	<10	92	<10	8	78
154	L30N 6050E	15	0.3	0.84	10	95	<5	1.16	<1	7	7	31	1.26	<10	0.14	349	<1	0.01	6	470	10	<5	<20	39	0.03	<10	28	<10	7	40
155	L30N 6075E	10	0.6	1.78	20	85	<5	1.20	2	9	11	70	1.91	<10	0.16	654	<1	0.02	16	850	8	<5	<20	40	0.04	<10	36	<10	17	78
156	L30N 6100E	10	0.3	1.89	30	65	<5	0.57	<1	6	15	30	2.10	<10	0.32	142	<1	0.01	9	390	6	<5	<20	22	0.06	<10	51	<10	12	40
157	L30N 6125E	10	0.6	2.33	35	95	<5	0.61	<1	14	35	57	3.75	<10	0.82	427	<1	0.03	26	480	8	<5	<20	28	0.12	<10	107	<10	11	126
158	L30N 6150E	20	0.2	2.51	20	110	<5	0.30	<1	12	44	47	3.96	<10	0.88	239	<1	0.03	21	350	6	<5	<20	22	0.13	<10	160	<10	7	91
159	L30N 6175E	5	0.5	2.39	10	115	<5	0.15	<1	12	44	36	4.16	<10	0.83	279	<1	0.02	20	500	10	<5	<20	11	0.15	<10	143	<10	6	95
160	L30N 6200E	10	1.3	2.68	25	70	<5	0.74	<1	11	24	60	3.30	<10	0.57	630	2	0.03	23	730	8	<5	<20	30	0.08	<10	93	<10	14	138
161	L30N 6225E	10	1.5	2.84	30	75	<5	0.60	3	13	30	118	3.18	<10	0.65	1120	2	0.03	31	850	4	<5	<20	27	0.08	<10	93	<10	30	97
162	L30N 6250E	10	1.0	3.11	30	105	<5	0.36	<1	12	23	31	3.31	<10	0.49	434	<1	0.02	18	760	8	<5	<20	16	0.11	<10	80	<10	14	105
163	L30N 6275E	10	0.2	2.11	35	90	<5	0.14	<1	12	33	43	5.28	<10	0.58	219	1	0.02	19	400	8	<5	<20	12	0.15	<10	134	<10	4	81
164	L30N 6300E	10	<0.2	2.62	50	100	<5	0.40	<1	18	38	62	4.52	<10	0.95	864	1	0.04	31	400	4	<5	<20	32	0.14	<10	151	<10	13	170
165	L30N 6325E	10	0.3	2.18	15	105	<5	0.21	<1	8	22	34	3.51	<10	0.46	155	<1	0.02	12	350	<2	<5	<20	18	0.12	<10	104	<10	6	61
166	L30N 6350E	5	0.5	3.15	25	55	<5	0.45	<1	9	11	33	2.15	<10	0.22	658	<1	0.02	10	620	10	<5	<20	19	0.09	<10	46	<10	18	64
167	L30N 6375E	5	0.4	2.39	25	75	<5	0.67	<1	16	33	47	3.77	<10	0.76	564	<1	0.03	22	510	8	<5	<20	27	0.15	<10	105	<10	17	96
168	L30N 6400E	10	0.3	3.57	20	105	<5	0.17	<1	17	37	54	4.04	<10	0.68	340	2	0.02	29	750	8	<5	<20	16	0.11	<10	118	<10	6	122
169	L30N 6425E	5	0.3	2.97	10	115	<5	0.10	1	10	28	31	3.53	<10	0.55	298	<1	0.02	14	1120	<2	<5	<20	13	0.10	<10	120	<10	5	62
170	L30N 6450E	5	0.9	2.20	15	90	<5	0.88	2	9	28	90	2.93	<10	0.68	878	3	0.02	24	1070	4	5	<20	30	0.04	<10	98	<10	14	95
171	L30N 6475E	5	0.5	2.86	15	185	<5	0.20	<1	17	42	58	4.10	<10	0.95	870	1	0.02	28	940	8	<5	<20	17	0.10	<10	128	<10	6	115
172	L30N 6500E	5	0.2	3.13	10	190	<5	0.18	<1	18	37	56	4.27	<10	0.88	879	<1	0.02	26	1510	10	<5	<20	14	0.12	<10	136	<10	7	125
173	L30N 6525E	5	<0.2	3.08	25	175	<5	0.18	<1	18	35	85	4.99	<10	1.16	440	<1	0.02	22	390	8	<5	<20	13	0.15	<10	163	<10	7	94
174	L30N 6550E	10	0.3	2.57	15	190	<5	0.20	1	20	52	67	4.88	<10	1.10	504	2	0.02	31	820	12	<5	<20	13	0.10	<10	159	<10	5	102
175	L30N 6600E	5	0.8	2.88	15	135	<5	0.14	<1	13	32	33	3.48	<10	0.61	435	<1	0.02	18	1750	10	<5	<20	14	0.10	<10	96	<10	4	86
176	L30N 6625E	5	0.2	2.87	15	155	<5	0.13	<1	14	38	45	4.42	<10	0.76	489	2	0.02	23	680	12	<5	<20	19	0.11	<10	140	<10	6	83
177	L30N 6650E	<5	0.8	2.85	20	175	<5	0.11	1	15	32	43	3.61	<10	0.58	2294	<1	0.02	20	1020	14	<5	<20	9	0.10	<10	108	<10	6	102
178	L30N 6675E	5	0.2	3.56	30	180	<5	0.19	<1	24	51	115	5.30	<10	1.32	512	<1	0.02	42	730	10	<5	<20	17	0.14	<10	154	<10	9	119
179	L30N 6700E	10	<0.2	3.59	20	200	<5	0.28	<1	24	62	117	5.79	<10	1.55	631	<1	0.02	44	1260	8	<5	<20	22	0.15	<10	181	<10	7	139
180	L30N 6725E	20	0.2	2.68	15	235	<5	0.46	1	24	48	70	5.27	<10	1.31	2483	<1	0.02	28	1070	10	<5	<20	33	0.12	<10	183	<10	4	139

06-Jul-05

ECO TECH LABORATORY LTD.

ICP CERTIFICATE OF ANALYSIS AK 2005-592

COLUMBIA YUKON EXPLORATIONS INC.

Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
181	L30N 6750E	10	0.4	3.18	20	150	<5	0.19	1	19	54	62	4.59	<10	1.15	956	2	0.02	34	910	14	<5	<20	13	0.12	<10	144	<10	9	120
182	L30N 6775E	15	0.4	3.40	20	160	<5	0.13	<1	19	38	52	4.38	<10	0.81	1156	2	0.02	25	1410	12	<5	<20	13	0.13	<10	122	<10	6	139
183	L30N 6800E	5	0.2	4.22	25	260	<5	0.31	<1	27	128	98	5.35	<10	1.55	850	<1	0.02	57	1040	12	<5	<20	22	0.20	<10	188	<10	12	104
184	L30N 6825E	40	<0.2	3.51	30	275	<5	0.40	<1	25	48	70	5.23	<10	1.13	1387	<1	0.03	33	1450	14	<5	<20	30	0.15	<10	161	<10	5	162
185	L30N 6850E	25	0.4	3.13	15	150	<5	0.24	<1	22	38	68	5.01	<10	0.95	514	<1	0.02	37	620	8	<5	<20	34	0.15	<10	113	<10	7	126
186	L30N 6875E	15	<0.2	2.33	25	135	<5	0.18	<1	15	18	25	3.51	<10	0.44	2377	<1	0.02	13	2180	16	<5	<20	17	0.10	<10	73	<10	3	127
187	L31N 5900E	30	0.3	3.40	30	145	<5	0.21	<1	20	48	56	4.08	<10	0.88	573	<1	0.03	33	830	12	<5	<20	27	0.14	<10	118	<10	9	144
188	L31N 5925E	20	0.2	3.13	25	180	<5	0.32	<1	22	54	57	5.30	<10	1.11	655	1	0.03	34	1130	8	<5	<20	33	0.14	<10	146	<10	7	129
189	L31N 5950E	5	0.6	3.42	40	160	<5	0.71	2	21	56	97	4.72	<10	1.30	1330	<1	0.04	64	590	10	<5	<20	49	0.16	<10	139	<10	26	143
190	L31N 5975E	5	0.4	2.48	15	180	5	0.12	<1	14	29	27	3.59	<10	0.58	745	<1	0.02	25	1650	14	<5	<20	10	0.13	<10	83	<10	6	103
191	L31N 6000E	5	0.2	3.07	20	205	<5	0.38	1	25	50	60	5.81	<10	1.37	1007	1	0.03	34	2080	12	<5	<20	30	0.15	<10	163	<10	5	159
192	L31N 6025E	5	0.3	2.84	25	130	<5	0.41	<1	19	41	68	4.69	<10	0.98	792	<1	0.03	28	640	12	<5	<20	28	0.16	<10	128	<10	12	146
193	L31N 6050E	5	0.4	2.82	30	125	<5	0.18	<1	16	35	56	4.86	<10	0.66	378	<1	0.02	21	540	10	<5	<20	14	0.17	<10	122	<10	7	81
194	L31N 6075E	5	<0.2	3.28	50	115	<5	0.19	<1	16	35	59	4.59	<10	0.81	355	1	0.02	28	880	8	<5	<20	17	0.13	<10	107	<10	7	97
195	L31N 6100E	5	<0.2	2.69	50	165	<5	0.25	<1	19	25	61	4.47	<10	0.70	1572	3	0.01	29	1060	20	<5	<20	18	0.08	<10	80	<10	11	121
196	L31N 6125E	10	0.4	2.83	30	70	<5	0.10	<1	11	22	24	3.60	<10	0.30	271	<1	0.02	13	2150	12	<5	<20	7	0.11	<10	74	<10	4	76
197	L31N 6150E	10	0.3	2.33	25	105	<5	0.58	<1	14	30	35	4.12	<10	0.66	455	<1	0.02	19	630	12	<5	<20	27	0.14	<10	92	<10	9	106
198	L31N 6175E	5	0.2	2.55	30	100	<5	0.45	1	18	29	56	4.01	<10	0.55	948	1	0.02	16	650	12	<5	<20	24	0.12	<10	88	<10	15	90
199	L31N 6200E	5	0.4	2.91	40	90	<5	0.59	1	18	32	80	4.16	<10	0.79	813	<1	0.03	31	880	16	<5	<20	30	0.11	<10	87	<10	21	179
200	L31N 6225E	5	0.4	2.44	15	150	<5	0.22	1	15	30	58	3.70	<10	0.65	726	2	0.02	20	560	10	<5	<20	18	0.09	<10	104	<10	6	99
201	L31N 6250E	5	0.5	3.60	15	225	<5	0.68	1	22	63	82	5.04	<10	1.31	1269	<1	0.04	39	1570	12	<5	<20	31	0.15	<10	203	<10	17	127
202	L31N 6275E	5	<0.2	2.29	30	60	<5	0.08	<1	7	12	18	3.43	<10	0.18	271	<1	0.01	7	2440	10	<5	<20	7	0.09	<10	58	<10	3	48
203	L31N 6300E	5	<0.2	3.26	15	55	<5	0.10	<1	10	19	16	3.09	<10	0.27	258	<1	0.02	9	480	10	<5	<20	8	0.15	<10	55	<10	9	51
204	L31N 6325E	5	0.3	2.49	15	130	<5	0.12	<1	15	22	22	3.54	<10	0.45	981	<1	0.02	14	610	12	<5	<20	13	0.16	<10	77	<10	7	99
205	L31N 6350E	5	0.3	1.12	10	65	<5	1.76	1	5	8	48	0.90	10	0.15	1580	2	0.01	12	960	10	<5	<20	54	0.02	<10	21	<10	25	24
206	L31N 6375E	5	0.4	2.54	10	120	<5	0.24	1	18	37	51	4.32	<10	0.75	1322	1	0.02	22	1190	12	<5	<20	19	0.11	<10	118	<10	4	118
207	L31N 6400E	10	0.2	3.09	25	105	<5	0.27	1	25	58	93	5.00	<10	1.32	990	<1	0.02	42	520	10	<5	<20	18	0.14	<10	137	<10	14	146
208	L31N 6425E	10	<0.2	3.02	25	130	<5	0.15	<1	15	37	65	4.17	<10	0.74	397	<1	0.02	25	1130	10	<5	<20	13	0.11	<10	102	<10	5	106
209	L31N 6450E	5	<0.2	3.01	25	145	<5	0.18	<1	22	42	77	4.46	<10	1.01	1202	2	0.02	32	1360	12	<5	<20	15	0.09	<10	114	<10	4	132
210	L31N 6475E	5	<0.2	2.99	15	95	<5	0.11	<1	14	35	64	4.19	<10	0.81	442	2	0.02	22	1580	10	<5	<20	12	0.09	<10	104	<10	3	98
211	L31N 6500E	5	0.2	2.61	10	140	<5	0.20	<1	22	46	66	5.15	<10	0.98	684	2	0.02	29	720	10	<5	<20	25	0.12	<10	130	<10	5	109
212	L31N 6525E	5	0.7	2.81	15	135	<5	0.11	<1	16	28	46	3.54	<10	0.57	723	1	0.02	22	1140	10	<5	<20	11	0.11	<10	82	<10	5	101
213	L31N 6550E	5	0.3	3.12	20	105	<5	0.16	<1	17	32	58	4.26	<10	0.73	490	3	0.02	29	2390	10	<5	<20	17	0.08	<10	98	<10	2	119
214	L31N 6575E	5	0.6	2.27	15	90	<5	0.20	<1	16	34	62	4.24	<10	0.87	683	3	0.01	35	1320	16	<5	<20	18	0.07	<10	92	<10	2	133
215	L31N 6600E	5	0.3	2.71	15	135	<5	0.15	<1	17	34	43	4.04	<10	0.62	871	1	0.02	19	1030	10	<5	<20	13	0.11	<10	95	<10	5	114

ECO TECH LABORATORY LTD.

ICP CERTIFICATE OF ANALYSIS AK 2005-592

COLUMBIA YUKON EXPLORATIONS INC.

Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
216	L31N 6625E	5	0.2	4.20	25	135	<5	0.16	<1	22	36	85	4.27	<10	0.91	511	<1	0.02	35	1280	8	<5	<20	31	0.12	<10	98	<10	8	120
217	L31N 6650E	5	0.6	2.74	25	120	<5	0.12	<1	22	21	67	4.00	<10	0.63	1731	<1	0.02	20	1040	14	<5	<20	10	0.10	<10	84	<10	2	138
218	L31N 6675E	5	0.2	2.97	20	140	<5	0.14	<1	18	37	58	4.30	<10	0.89	761	1	0.02	25	1760	12	<5	<20	15	0.10	<10	103	<10	3	121
219	L31N 6700E	5	0.6	2.44	15	165	<5	0.32	<1	21	44	77	5.75	<10	1.25	1206	1	0.01	23	2270	10	<5	<20	32	0.09	<10	125	<10	<1	118
220	L31N 6725E	5	<0.2	3.25	15	165	<5	0.39	<1	21	50	69	5.47	<10	1.60	992	3	0.03	30	1620	8	<5	<20	19	0.11	<10	158	<10	6	138
221	L31N 6750E	5	0.4	2.67	40	150	<5	0.31	3	22	27	76	4.89	<10	0.74	727	2	0.01	31	840	12	<5	<20	26	0.12	<10	85	<10	11	198
222	L31N 6775E	5	0.3	1.85	35	115	<5	0.13	<1	12	26	36	4.61	<10	0.56	393	2	0.01	21	930	14	<5	<20	11	0.11	<10	87	<10	3	116
223	L31N 6800E	<5	0.3	3.18	25	160	<5	0.28	<1	24	44	85	5.15	<10	1.10	973	<1	0.02	37	650	14	<5	<20	26	0.15	<10	118	<10	8	120
224	L31N 6825E	<5	0.2	2.63	25	160	<5	0.22	<1	18	27	51	4.46	<10	0.62	910	<1	0.02	17	2100	8	<5	<20	27	0.12	<10	86	<10	3	108
225	L31N 6850E	<5	0.2	2.03	5	70	<5	0.33	<1	14	28	19	4.06	<10	0.89	1004	<1	0.02	11	820	8	<5	<20	31	0.15	<10	93	<10	8	80
226	L31N 6875E	5	0.2	2.65	20	95	<5	0.26	<1	17	34	43	3.98	<10	0.86	738	<1	0.02	20	570	10	<5	<20	27	0.12	<10	96	<10	7	85
227	L32N 6400E	5	0.2	2.12	10	120	<5	0.25	<1	11	19	17	3.18	<10	0.40	1335	<1	0.02	10	840	18	<5	<20	13	0.15	<10	65	<10	6	74
228	L32N 6425E	<5	<0.2	3.00	15	80	<5	0.11	<1	15	23	28	3.33	<10	0.40	654	<1	0.02	13	1490	8	<5	<20	7	0.15	<10	67	<10	8	84
229	L32N 6450E	5	0.3	2.34	10	90	<5	0.09	<1	11	20	29	3.76	<10	0.45	644	<1	0.01	14	1280	10	<5	<20	8	0.13	<10	74	<10	5	74
230	L32N 6475E	5	0.4	2.89	25	125	<5	0.21	<1	16	30	51	3.73	<10	0.71	642	1	0.02	27	970	8	<5	<20	16	0.12	<10	86	<10	7	98
231	L32N 6500E	5	0.2	2.67	25	155	<5	0.20	<1	18	35	64	3.97	<10	0.80	839	<1	0.02	31	1150	10	<5	<20	17	0.11	<10	88	<10	6	119
232	L32N 6525E	5	0.6	2.54	20	125	<5	0.37	3	30	38	70	4.12	<10	1.04	3771	3	0.02	31	890	10	<5	<20	19	0.09	<10	94	<10	24	162
233	L32N 6575E	5	0.2	2.59	15	90	<5	0.12	<1	17	28	55	4.22	<10	0.70	1101	2	0.01	22	1230	12	<5	<20	8	0.11	<10	92	<10	4	94
234	L32N 6600E	5	0.6	3.06	20	90	<5	0.28	1	16	30	47	4.15	<10	0.88	671	3	0.02	24	1620	8	<5	<20	12	0.10	<10	102	<10	6	131
235	L32N 6625E	5	0.3	1.89	5	85	<5	0.24	<1	14	50	36	4.11	<10	1.26	643	<1	0.02	16	660	8	<5	<20	20	0.11	<10	113	<10	5	81
236	L32N 6650E	<5	0.2	1.89	10	130	<5	0.33	<1	24	35	29	4.50	<10	0.79	2324	<1	0.02	12	830	20	<5	<20	31	0.11	<10	95	<10	7	100
237	L32N 6675E	<5	0.2	1.80	10	100	<5	0.22	<1	15	22	22	3.14	<10	0.37	1209	2	0.02	7	1350	8	<5	<20	22	0.07	<10	55	<10	7	88
238	L32N 6700E	5	0.2	2.62	10	245	10	0.43	2	20	44	74	6.50	<10	1.51	1522	<1	0.02	19	1030	4	<5	<20	33	0.15	<10	185	<10	2	120
239	L32N 6725E	<5	<0.2	1.55	10	100	<5	0.32	<1	8	19	15	3.03	<10	0.30	161	<1	0.01	7	290	8	<5	<20	37	0.10	<10	61	<10	3	49
240	L32N 6750E	30	0.4	3.33	20	80	<5	0.29	<1	11	18	17	3.00	<10	0.32	224	<1	0.02	8	960	10	<5	<20	32	0.13	<10	53	<10	8	62
241	L32N 6775E	5	0.3	2.78	30	75	<5	0.09	<1	10	16	23	2.99	<10	0.27	467	<1	0.02	9	1340	14	<5	<20	11	0.11	<10	54	<10	6	74
242	L32N 6800E	<5	0.2	2.83	20	90	<5	0.14	<1	10	16	14	2.55	<10	0.27	831	<1	0.02	8	1400	12	<5	<20	14	0.12	<10	49	<10	7	60
243	L32N 6825E	10	0.4	2.36	40	90	<5	0.10	<1	12	18	30	3.60	<10	0.38	278	2	0.01	14	420	20	<5	<20	8	0.08	<10	62	<10	4	122
244	L32N 6850E	5	0.5	1.73	55	100	<5	0.07	<1	11	20	36	4.49	<10	0.54	431	5	<0.01	18	790	20	<5	<20	6	0.04	<10	68	<10	<1	151
245	L32N 6875E	15	<0.2	3.28	115	105	<5	0.58	<1	11	19	15	3.02	<10	0.46	1068	<1	0.02	8	1420	14	<5	<20	72	0.10	<10	57	<10	5	88
246	L33N 6400E	10	0.2	3.05	70	95	5	0.20	<1	14	39	61	4.58	<10	0.84	438	<1	0.02	23	820	8	<5	<20	21	0.14	<10	139	<10	8	89
247	L33N 6425E	5	0.2	2.84	20	65	<5	0.08	<1	7	15	23	4.54	<10	0.24	191	<1	0.01	5	1200	10	<5	<20	8	0.16	<10	75	<10	5	33
248	L33N 6450E	5	<0.2	2.05	15	60	<5	0.12	<1	10	24	19	3.59	<10	0.48	212	<1	0.02	9	460	12	<5	<20	9	0.16	<10	104	<10	7	48
249	L33N 6475E	5	1.0	1.92	55	110	<5	0.10	1	19	19	60	4.05	50	0.44	386	5	0.01	23	580	18	<5	<20	10	0.05	<10	60	<10	##	128
250	L33N 6500E	5	0.7	2.61	25	80	<5	0.07	<1	10	14	25	3.16	<10	0.31	425	<1	0.02	11	930	20	<5	<20	10	0.11	<10	59	<10	6	89
251	L33N 6525E	5	<0.2	2.20	10	80	5	0.11	<1	8	12	13	3.59	<10	0.20	255	<1	0.01	5	1280	18	<5	<20	20	0.16	<10	67	<10	5	48
252	L33N 6550E	5	0.2	2.38	15	55	<5	0.10	<1	8	9	13	2.87	<10	0.28	183	<1	0.02	6	760	12	<5	<20	15	0.15	<10	60	<10	8	59
253	L33N 6575E	5	0.3	2.06	105	110	<5	0.93	2	14	20	31	3.11	<10	0.62	2221	1	0.03	13	730	14	<5	<20	45	0.07	<10	70	<10	11	113
254	L33N 6600E	5	0.2	2.36	25	120	<5	0.47	<1	16	23	25	4.46	<10	0.81	989	<1	0.02	11	2060	6	<5	<20	36	0.12	<10	93	<10	4	103
255	L33N 6625E	10	0.2	1.47	15	85	<5	0.26	<1	9	9	12	3.29	<10	0.27	351	<1	0.02	5	1830	10	<5	<20	21	0.12	<10	65	<10	4	69

06-Jul-05

ECO TECH LABORATORY LTD.

ICP CERTIFICATE OF ANALYSIS AK 2005-592

COLUMBIA YUKON EXPLORATIONS INC.

Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
256	L33N 6650E	5 <0.2	1.09	10	60	<5	0.21	<1	9	17	13	3.27	<10	0.38	288	<1	0.01	5	1010	18	<5	<20	20	0.16	<10	72	<10	6	49	
257	L33N 6675E	5 <0.2	2.23	20	70	5	0.12	<1	8	22	26	3.20	<10	0.38	194	<1	0.01	8	500	12	<5	<20	13	0.13	<10	85	<10	6	45	
258	L33N 6700E	5 0.8	1.63	10	55	5	0.14	<1	7	13	14	2.39	<10	0.29	266	<1	0.01	6	810	18	<5	<20	12	0.08	<10	52	<10	4	42	
259	L33N 6725E	5 <0.2	2.42	20	65	<5	0.14	<1	10	21	16	3.06	<10	0.37	621	<1	0.02	9	1230	12	<5	<20	12	0.13	<10	69	<10	6	68	
260	L33N 6750E	5 0.3	2.11	35	95	<5	0.16	<1	10	11	21	2.69	<10	0.22	877	2	0.02	10	490	20	<5	<20	9	0.09	<10	50	<10	5	81	
261	L33N 6775E	10 0.8	2.35	20	80	<5	0.33	<1	14	14	24	3.35	<10	0.30	478	<1	0.02	10	590	12	<5	<20	29	0.11	<10	74	<10	7	76	
262	L33N 6800E	5 0.4	2.71	20	65	<5	0.14	<1	7	9	11	2.54	<10	0.11	132	<1	0.01	5	650	12	<5	<20	17	0.13	<10	54	<10	6	46	
263	L33N 6825E	5 0.3	2.35	10	60	<5	0.17	<1	9	11	19	2.36	<10	0.27	387	<1	0.02	6	570	16	<5	<20	21	0.13	<10	57	<10	6	67	
264	L33N 6850E	10 0.4	2.90	20	80	<5	0.30	<1	12	12	30	3.02	<10	0.35	724	<1	0.01	6	940	40	<5	<20	35	0.11	<10	65	<10	5	150	
265	L33N 6875E	5 0.3	2.60	25	115	<5	0.30	<1	7	11	18	2.12	<10	0.23	597	<1	0.02	7	1250	14	<5	<20	29	0.08	<10	48	<10	4	48	

QC DATA:**Repeat:**

1	L26N 6100E	30	0.2	2.70	60	85	<5	0.21	<1	19	32	58	3.87	<10	0.43	442	1	0.02	32	1510	6	<5	<20	26	0.11	<10	113	<10	6	78
2	L26N 6125E	100																												
10	L26N 6325E	10	0.3	4.24	45	85	<5	0.09	<1	17	18	80	4.02	<10	0.38	194	<1	0.02	18	700	6	<5	<20	12	0.16	<10	95	<10	17	74
19	L26N 6550E	10	0.3	2.27	60	70	<5	0.17	<1	16	23	54	4.34	<10	0.56	529	2	0.01	17	2030	8	<5	<20	16	0.08	<10	96	<10	3	79
28	L26N 6775E	5 0.2	2.84	20	105	<5	0.39	<1	22	28	59	4.17	<10	0.53	1180	1	0.02	40	1580	6	<5	<20	34	0.08	<10	98	<10	6	88	
36	L27N 6025E	5 <0.2	2.81	15	55	<5	0.10	<1	8	12	19	2.74	<10	0.22	286	<1	0.02	8	1380	10	<5	<20	12	0.10	<10	62	<10	6	67	
38	L27N 6075E	45																												
45	L27N 6250E	10 0.2	1.83	10	115	<5	0.45	<1	18	56	43	3.56	<10	0.78	1295	1	0.07	39	1080	4	<5	<20	43	0.09	<10	102	<10	12	75	
54	L27N 6475E	15 0.3	2.69	20	70	<5	0.27	<1	29	27	160	5.56	<10	0.90	510	3	0.03	43	1150	<2	<5	<20	35	0.06	<10	116	<10	1	86	
63	L27N 6700E	5 <0.2	3.06	20	110	<5	0.19	<1	17	26	56	3.26	<10	0.54	774	<1	0.02	24	1090	8	<5	<20	19	0.10	<10	95	<10	6	73	
71	L28N 5900E	15 0.4	2.65	25	125	<5	0.22	<1	14	37	45	3.67	<10	0.65	758	1	0.03	20	1090	8	<5	<20	18	0.11	<10	136	<10	6	96	
76	L28N 6050E	40																												
80	L28N 6150E	10 0.4	2.36	20	125	<5	0.28	<1	17	21	64	3.92	<10	0.68	1077	<1	0.02	16	1420	10	<5	<20	22	0.11	<10	111	<10	4	105	
89	L28N 6375E	10 0.2	2.52	25	140	<5	0.18	<1	21	29	50	3.75	<10	0.94	746	<1	0.03	21	650	10	<5	<20	14	0.16	<10	123	<10	7	99	
94	L28N 6550E	40																												
98	L28N 6650E	5 0.2	2.93	20	150	<5	0.18	<1	19	55	53	4.73	<10	1.02	523	<1	0.03	29	530	4	<5	<20	16	0.17	<10	162	<10	8	101	
106	L28N 6850E	5 <0.2	2.96	25	90	<5	0.14	<1	14	18	17	3.50	<10	0.41	398	<1	0.02	10	660	12	<5	<20	8	0.17	<10	82	<10	9	80	
115	L29N 6075E	25 0.2	2.95	40	95	<5	0.27	<1	15	33	25	3.55	<10	0.67	497	<1	0.03	14	1240	6	<5	<20	18	0.11	<10	106	<10	7	118	
117	L29N 6125E	35																												
118	L29N 6150E	25																												
124	L29N 6300E	10 0.2	1.23	10	105	<5	0.16	<1	10	9	44	2.65	<10	0.23	793	<1	0.01	8	1320	10	<5	<20	12	0.07	<10	60	<10	2	56	
133	L29N 6525E	5 0.3	3.57	15	120	<5	0.42	<1	18	42	60	4.54	<10	0.86	680	<1	0.03	28	560	4	<5	<20	22	0.15	<10	157	<10	12	120	
141	L29N 6725E	5 0.2	3.75	20	125	<5	0.17	<1	14	19	32	3.34	<10	0.65	553	1	0.02	14	1520	10	<5	<20	12	0.12	<10	98	<10	7	77	
150	L30N 5950E	10 0.3	2.83	35	110	<5	0.13	<1	14	31	57	3.06	<10	0.58	460	<1	0.02	14	860	8	<5	<20	18	0.11	<10	93	<10	6	60	
151	L30N 5975E	45																												
159	L30N 6175E	10 0.6	2.38	10	110	<5	0.16	<1	12	44	37	4.10	<10	0.83	282	<1	0.02	22	520	8	<5	<20	11	0.15	<10	143	<10	7	97	
168	L30N 6400E	5 0.3	3.47	20	105	<5	0.17	<1	17	37	53	4.05	<10	0.68	338	2	0.02	28	730	10	<5	<20	15	0.11	<10	117	<10	6	124	
176	L30N 6625E	5 0.2	2.92	15	140	<5	0.13	<1	13	38	45	4.35	<10	0.80	505	1	0.02	22	650	8	<5	<20	15	0.12	<10	142	<10	7	84	

06-Jul-05

ECO TECH LABORATORY LTD.

ICP CERTIFICATE OF ANALYSIS AK 2005-592

COLUMBIA YUKON EXPLORATIONS INC.

Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
184	L30N 6825E	25																												
185	L30N 6850E	25	0.5	3.04	15	150	<5	0.26	1	21	38	66	4.91	<10	0.96	514	<1	0.02	34	640	14	<5	<20	29	0.16	<10	114	<10	9	122
187	L31N 5900E	30																												
194	L31N 6075E	5	0.2	3.36	45	115	<5	0.22	<1	15	33	61	4.54	<10	0.82	342	<1	0.02	26	940	4	<5	<20	21	0.13	<10	107	<10	8	94
203	L31N 6300E	5 <0.2	3.13	20	60	<5	0.11	<1	10	19	15	3.01	<10	0.28	247	<1	0.02	8	450	14	<5	<20	9	0.16	<10	56	<10	10	53	
211	L31N 6500E	5	0.2	2.65	15	140	<5	0.20	1	22	46	65	5.13	<10	0.99	671	3	0.02	30	720	8	<5	<20	24	0.12	<10	130	<10	5	108
220	L31N 6725E	5 <0.2	3.29	10	165	<5	0.40	<1	21	50	68	5.41	<10	1.61	957	3	0.03	29	1600	<2	<5	<20	19	0.11	<10	158	<10	6	140	
229	L32N 6450E	5	0.4	2.27	15	95	<5	0.10	<1	11	20	28	3.73	<10	0.44	622	<1	0.01	13	1300	12	<5	<20	7	0.14	<10	72	<10	5	74
238	L32N 6700E	5	0.2	2.54	10	235	<5	0.41	1	20	42	72	6.29	<10	1.46	1450	<1	0.01	19	1010	10	<5	<20	30	0.14	<10	182	<10	4	117
240	L32N 6750E	30																												
246	L33N 6400E	5 <0.2	3.04	70	85	<5	0.20	<1	14	38	61	4.45	<10	0.83	435	<1	0.02	21	810	6	<5	<20	18	0.14	<10	137	<10	9	86	
255	L33N 6625E	10	0.2	1.42	15	85	5	0.27	<1	9	9	11	3.19	<10	0.25	365	<1	0.02	5	1860	12	<5	<20	19	0.12	<10	63	<10	5	71

Standard:

GEO '05	140	1.5	1.43	60	145	<5	1.26	<1	15	55	84	3.64	<10	0.75	558	<1	0.03	27	610	18	<5	<20	48	0.11	<10	69	<10	10	74
GEO '05	140	1.5	1.42	55	140	<5	1.23	<1	15	58	82	3.55	<10	0.74	544	<1	0.03	25	570	20	<5	<20	43	0.18	<10	68	<10	9	73
GEO '05	135	1.5	1.38	55	140	<5	1.21	<1	15	57	81	3.52	<10	0.73	531	<1	0.02	23	540	22	<5	<20	43	0.11	<10	67	<10	9	74
GEO '05	135	1.5	1.31	50	130	<5	1.17	<1	14	49	84	3.34	<10	0.71	515	<1	0.02	23	540	22	<5	<20	42	0.10	<10	73	<10	8	73
GEO '05	130	1.5	1.40	60	140	<5	1.23	<1	15	53	84	3.55	<10	0.73	536	<1	0.03	25	560	20	<5	<20	43	0.11	<10	67	<10	9	77
GEO '05	135	1.5	1.38	55	145	<5	1.27	<1	15	53	83	3.64	<10	0.74	555	<1	0.02	26	590	20	<5	<20	42	0.11	<10	67	<10	10	76
GEO '05	135	1.4	1.44	55	150	<5	1.32	<1	16	56	83	3.70	<10	0.76	563	<1	0.03	25	590	20	<5	<20	49	0.11	<10	72	<10	11	76
GEO '05	140	1.4	1.49	55	150	<5	1.30	<1	16	56	86	3.71	<10	0.78	561	<1	0.03	25	580	22	<5	<20	47	0.10	<10	71	<10	10	76
GEO '05	135	1.5	1.47	55	150	<5	1.30	<1	16	55	88	3.73	<10	0.79	570	<1	0.03	25	570	20	<5	<20	47	0.11	<10	71	<10	11	77

22-Jul-05

ECO TECH LABORATORY LTD.
 10041 Dallas Drive
KAMLOOPS, B.C.
 V2C 6T4

Phone: 250-573-5700
 Fax : 250-573-4557

ICP CERTIFICATE OF ANALYSIS AK 2005-677

COLUMBIA YUKON EXPLORATIONS INC.
 5936 Stafford Road
Nelson, BC
 V1L 6P3

ATTENTION: Bernie Augsten / Gillian Feyer*No. of samples received: 154**Sample type: Soil**Project #: Barnes Creek**Shipment #:not indicated'**Samples submitted by: Bernhardt Augsten***Values in ppm unless otherwise reported**

Et #.	Tag #	Au(ppb)	Aq	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
1	HR 1	10	0.5	2.40	40	110	<5	0.16	<1	8	15	26	2.78	<10	0.20	890	1	0.02	10	1030	28	<5	<20	12	0.08	<10	57	<10	3	79
2	HR 2	15	0.5	3.16	90	60	<5	0.40	<1	17	17	48	3.90	<10	0.62	659	<1	0.03	12	1880	18	<5	<20	42	0.11	<10	114	<10	4	72
3	HR 3	125	0.5	3.26	90	65	<5	0.22	<1	13	25	46	3.67	<10	0.43	588	<1	0.02	17	990	18	<5	<20	17	0.13	<10	102	<10	7	74
4	HR 4	25	0.6	3.09	70	50	<5	0.36	<1	13	24	63	3.14	<10	0.36	276	<1	0.02	23	710	12	10	<20	34	0.15	<10	86	<10	14	63
5	HR 6	135	0.5	2.82	120	70	<5	0.59	<1	11	28	44	2.75	<10	0.42	777	<1	0.02	19	980	22	5	<20	35	0.10	<10	78	<10	8	62
6	HR 7	25	0.6	2.43	60	70	<5	0.50	<1	9	20	24	3.17	<10	0.26	370	<1	0.02	12	680	14	<5	<20	24	0.13	<10	77	<10	6	57
7	HR 8	15	0.6	2.37	65	85	<5	0.49	<1	11	21	43	3.13	<10	0.31	639	<1	0.02	19	860	26	<5	<20	29	0.12	<10	90	<10	9	63
8	HR 9	15	0.2	3.14	30	65	<5	0.32	<1	9	24	41	3.55	<10	0.29	160	<1	0.02	16	930	14	<5	<20	25	0.13	<10	88	<10	9	57
9	HR 10	10	0.8	2.46	225	85	<5	1.40	<1	12	21	39	2.65	<10	0.31	1223	2	0.02	26	1100	18	10	<20	58	0.06	<10	63	<10	9	84
10	HR 11	40	0.6	4.05	55	60	<5	0.77	<1	19	22	67	4.12	<10	0.24	351	3	0.02	33	1290	6	<5	<20	65	0.09	<10	83	<10	11	62
11	HR 12	5	0.3	3.37	20	65	<5	0.15	<1	8	22	33	3.03	<10	0.16	266	<1	0.02	13	1070	12	<5	<20	11	0.10	<10	77	<10	5	62
12	HR 14	10	0.5	4.36	25	75	<5	0.55	<1	14	27	54	3.49	<10	0.24	354	2	0.02	34	1600	12	<5	<20	50	0.08	<10	79	<10	9	71
13	HR 15	10	0.4	2.99	35	75	<5	0.34	<1	12	24	39	3.06	<10	0.26	467	<1	0.02	22	1110	18	<5	<20	29	0.12	<10	93	<10	10	60
14	HR 16	5	0.3	4.17	45	70	<5	0.45	<1	16	28	66	3.11	<10	0.39	365	<1	0.03	31	950	8	<5	<20	42	0.14	<10	91	<10	22	59
15	HR 17	5	0.4	3.19	25	100	<5	0.26	<1	13	30	43	3.22	<10	0.39	709	<1	0.03	28	1390	12	<5	<20	24	0.12	<10	92	<10	7	58
16	HR 18	10	<0.2	4.19	35	80	<5	0.17	<1	16	27	49	3.37	<10	0.46	456	<1	0.02	22	930	12	<5	<20	12	0.14	<10	93	<10	13	90
17	HR 19	10	0.2	4.18	35	130	<5	0.18	<1	16	36	56	3.91	<10	0.67	647	<1	0.02	26	810	12	<5	<20	15	0.13	<10	112	<10	11	122
18	HR 20	5	0.2	3.09	15	80	<5	0.14	<1	10	18	26	3.03	<10	0.32	299	<1	0.02	10	950	12	<5	<20	11	0.15	<10	92	<10	5	68
19	HR 21	10	0.3	3.82	50	75	<5	0.25	<1	11	23	37	2.86	<10	0.35	273	<1	0.10	17	820	26	<5	<20	24	0.10	<10	80	<10	8	80
20	HR 22	5	0.2	3.01	30	95	<5	0.54	1	18	69	33	3.06	<10	0.49	1172	<1	0.07	58	890	14	15	<20	45	0.13	<10	82	<10	18	64
21	HR 23	35	1.2	3.26	305	95	<5	1.07	1	17	27	229	3.09	<10	0.37	1438	1	0.06	51	920	14	10	<20	41	0.08	<10	71	<10	29	86
22	HR 24	35	0.2	3.42	155	110	<5	0.28	<1	17	25	57	4.99	<10	0.73	373	<1	0.06	18	710	8	<5	<20	19	0.17	<10	153	<10	7	96
23	HR 25	5	<0.2	4.52	30	75	<5	0.41	<1	20	28	58	4.10	<10	0.52	467	<1	0.07	33	1580	12	<5	<20	37	0.12	<10	98	<10	5	100
24	HR 26	5	0.3	4.33	40	110	<5	0.24	<1	22	34	53	3.73	<10	0.46	544	<1	0.07	33	1100	18	<5	<20	19	0.14	<10	87	<10	11	103
25	HR 27	25	1.6	3.13	215	100	<5	0.98	<1	23	55	329	4.39	<10	0.90	976	<1	0.07	63	720	14	<5	<20	45	0.10	<10	127	<10	57	145
26	HR 28	20	1.3	2.56	140	80	<5	1.53	3	15	39	227	2.98	<10	0.53	1020	1	0.07	42	890	14	<5	<20	57	0.07	<10	84	<10	24	95
27	HR 29	5	0.5	3.31	90	70	<5	0.68	<1	19	36	68	4.59	<10	0.74	482	<1	0.06	30	680	18	<5	<20	33	0.15	<10	122	<10	17	102
28	HR 30	15	0.6	3.77	60	60	<5	0.72	1	20	32	73	4.05	<10	0.64	631	<1	0.07	36	780	18	<5	<20	34	0.13	<10	105	<10	20	132
29	HR 31	10	0.2	3.60	65	95	<5	0.29	<1	21	39	93	4.72	<10	0.93	482	<1	0.06	39	840	18	<5	<20	21	0.14	<10	130	<10	13	99
30	HR 32	10	0.5	3.51	45	95	<5	0.93	1	21	41	106	4.40	<10	0.99	1923	<1	0.09	49	850	14	<5	<20	49	0.13	<10	137	<10	16	107

22-Jul-05

ECO TECH LABORATORY LTD.

ICP CERTIFICATE OF ANALYSIS AK 2005-677

COLUMBIA YUKON EXPLORATIONS INC.

Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
31	HR 33	15	0.3	3.78	40	65	<5	0.36	<1	18	26	49	3.92	<10	0.56	437	<1	0.07	30	1280	14	10	<20	30	0.12	<10	97	<10	10	64
32	HR 34	10	0.5	3.91	95	60	<5	0.67	<1	21	28	81	4.71	<10	0.50	410	2	0.07	40	840	14	5	<20	52	0.11	<10	105	<10	21	68
33	HR 35	10	0.8	4.56	215	40	<5	0.76	<1	19	29	94	4.96	<10	0.51	288	2	0.07	34	710	8	<5	<20	31	0.10	<10	106	<10	14	55
34	HR 36	5	0.2	2.37	40	65	<5	0.35	<1	18	40	80	4.61	<10	0.74	415	<1	0.06	30	630	12	<5	<20	23	0.13	<10	133	<10	8	103
35	HR 37	40	0.7	2.59	115	100	<5	0.44	1	18	25	75	3.94	<10	0.61	799	2	0.05	28	1120	20	<5	<20	25	0.09	<10	91	<10	11	100
36	HR 38	10	0.3	3.30	35	105	<5	0.24	<1	21	33	89	4.31	<10	0.75	540	<1	0.03	34	900	18	<5	<20	19	0.13	<10	106	<10	12	96
37	L32N 5900E	5	0.4	2.71	15	155	<5	0.46	<1	18	36	52	4.06	<10	0.80	922	<1	0.02	25	1130	18	<5	<20	39	0.14	<10	123	<10	7	112
38	L32N 5925E	5	0.5	3.42	15	190	<5	0.39	<1	24	57	80	5.40	<10	1.39	903	<1	0.03	35	1090	18	<5	<20	46	0.18	<10	181	<10	9	142
39	L32N 5950E	5	0.4	3.38	40	175	<5	0.26	<1	25	54	81	5.60	<10	1.44	1575	<1	0.02	42	1380	18	<5	<20	20	0.18	<10	171	<10	6	140
40	L32N 5975E	10	0.3	2.89	45	140	<5	0.24	<1	19	53	75	5.54	<10	1.28	877	<1	0.02	30	1310	14	<5	<20	18	0.15	<10	182	<10	6	133
41	L32N 6000E	5	0.2	2.46	35	135	<5	0.11	<1	15	26	29	4.73	<10	0.46	568	<1	0.02	12	730	14	<5	<20	12	0.18	<10	122	<10	3	91
42	L32N 6025E	10	0.3	2.76	95	125	<5	0.17	<1	20	38	33	5.26	<10	0.78	601	<1	0.02	22	730	14	<5	<20	15	0.18	<10	134	<10	7	116
43	L32N 6050E	5	0.9	4.00	125	85	<5	0.10	<1	13	27	50	4.27	<10	0.42	253	<1	0.09	19	560	22	<5	<20	8	0.18	<10	81	<10	12	66
44	L32N 6075E	10	0.6	2.64	65	130	<5	0.23	<1	16	28	37	4.93	<10	0.58	738	2	0.05	20	1480	14	<5	<20	19	0.13	<10	106	<10	3	96
45	L32N 6100E	10	<0.2	2.12	20	100	<5	0.11	<1	12	19	26	3.47	<10	0.32	711	<1	0.06	10	1240	18	<5	<20	11	0.15	<10	81	<10	5	103
46	L32N 6125E	10	0.2	3.14	50	100	5	0.51	<1	21	36	53	4.53	<10	0.94	2281	2	0.02	23	630	8	<5	<20	32	0.14	<10	116	<10	25	119
47	L32N 6150E	5	0.3	2.68	15	80	<5	0.13	<1	7	12	19	2.76	<10	0.22	719	<1	0.04	8	1010	12	<5	<20	8	0.12	<10	55	<10	3	59
48	L32N 6175E	20	0.2	2.64	45	55	<5	0.06	<1	6	12	21	2.89	<10	0.17	150	<1	0.05	7	1340	18	<5	<20	4	0.11	<10	58	<10	6	41
49	L32N 6200E	10	0.3	1.35	<5	115	<5	0.59	<1	9	7	22	2.61	<10	0.07	130	<1	0.05	6	340	14	<5	<20	32	0.13	<10	49	<10	14	30
50	L32N 6225E	5	0.2	1.10	5	90	<5	0.22	<1	6	15	22	2.84	<10	0.21	153	<1	0.05	7	490	14	<5	<20	23	0.11	<10	65	<10	3	43
51	L32N 6250E	5	<0.2	2.28	15	65	<5	0.11	<1	9	18	21	3.51	<10	0.28	183	<1	0.05	12	540	20	<5	<20	10	0.15	<10	68	<10	5	85
52	L32N 6275E	50	0.4	2.12	35	85	<5	0.14	<1	22	27	58	4.50	<10	0.50	1258	3	0.07	16	1230	18	<5	<20	12	0.13	<10	94	<10	3	80
53	L32N 6300E	10	0.2	2.31	20	145	<5	0.45	<1	21	33	36	4.51	<10	0.60	664	<1	0.05	16	530	12	<5	<20	45	0.16	<10	104	<10	5	83
54	L32N 6325E	105	0.3	2.56	35	220	<5	0.52	<1	14	27	35	3.53	<10	0.58	848	<1	0.06	18	1040	28	<5	<20	29	0.13	<10	86	<10	4	124
55	L32N 6350E	5	0.3	2.44	10	120	<5	0.22	<1	17	23	33	3.80	<10	0.50	2312	<1	0.02	12	820	12	<5	<20	17	0.15	<10	92	<10	5	91
56	L32N 6375E	5	0.3	2.88	20	125	<5	0.24	<1	17	30	42	3.82	<10	0.60	1267	<1	0.02	17	1030	12	<5	<20	17	0.17	<10	96	<10	8	81
57	L33N 5900E	5	0.8	2.33	25	125	<5	0.20	<1	17	30	60	4.42	<10	0.84	871	<1	0.02	27	980	14	<5	<20	22	0.14	<10	103	<10	4	113
58	L33N 5925E	5	0.2	2.26	10	145	<5	0.30	<1	15	36	44	4.96	<10	1.17	424	<1	0.02	22	660	6	<5	<20	43	0.24	<10	135	<10	6	69
59	L33N 5950E	5	1.5	3.12	25	105	<5	0.80	3	16	33	165	3.92	<10	0.81	989	<1	0.03	56	470	<2	<5	<20	41	0.16	<10	104	<10	34	82
60	L33N 5975E	5	0.2	2.60	25	115	<5	0.17	<1	17	30	45	4.26	<10	0.59	472	<1	0.05	23	580	20	<5	<20	19	0.16	<10	115	<10	8	107
61	L33N 6000E	15	0.3	3.76	40	230	<5	0.29	1	22	59	84	5.57	<10	1.56	1218	<1	0.02	40	1280	6	<5	<20	24	0.16	<10	166	<10	9	166
62	L33N 6025E	5	0.5	3.51	25	120	<5	0.18	<1	19	37	52	4.98	<10	0.89	590	<1	0.05	24	1470	12	<5	<20	14	0.16	<10	123	<10	6	99
63	L33N 6050E	10	1.4	3.31	30	75	<5	0.28	1	17	36	58	4.71	<10	0.94	612	2	0.02	22	1210	8	<5	<20	20	0.15	<10	122	<10	8	93
64	L33N 6075E	30	0.6	3.63	30	190	<5	0.16	<1	17	31	56	3.92	<10	0.68	850	<1	0.02	26	1000	6	<5	<20	16	0.14	<10	99	<10	8	113
65	L33N 6100E	10	0.3	3.06	35	130	<5	0.21	<1	15	41	44	5.06	<10	1.04	511	<1	0.02	23	370	4	<5	<20	22	0.20	<10	139	<10	9	95
66	L33N 6125E	5	0.6	2.21	20	150	<5	0.40	2	8	15	27	3.48	<10	0.23	162	<1	0.07	7	290	12	<5	<20	30	0.18	<10	80	<10	9	61
67	L33N 6150E	5	0.7	2.75	25	100	<5	0.16	<1	10	13	16	2.87	<10	0.15	1000	<1	0.05	10	1100	26	<5	<20	10	0.11	<10	49	<10	4	92
68	L33N 6175E	10	0.2	2.64	20	95	<5	0.67	<1	14	23	36	4.35	<10	0.68	580	<1	0.06	12	1370	12	<5	<20	78	0.11	<10	98	<10	4	72
69	L33N 6200E	5	<0.2	3.81	20	50	5	0.10	<1	6	13	18	2.89	<10	0.18	135	<1	0.05	8	1250	12	<5	<20	10	0.13	<10	54	<10	5	42
70	L33N 6225E	5	<0.2	2.58	20	80	<5	0.26	<1	17	23	34	3.55	<10	0.47	632	<1	0.05	15	990	20	<5	<20	28	0.14	<10	75	<10	7	69

ECO TECH LABORATORY LTD.

ICP CERTIFICATE OF ANALYSIS AK 2005-677

COLUMBIA YUKON EXPLORATIONS INC.

Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
71	L33N 6250E	5	0.2	2.57	15	95	<5	0.24	<1	10	20	30	2.32	<10	0.41	268	<1	0.07	10	680	18	<5	<20	16	0.14	<10	67	<10	9	55
72	L33N 6275E	5	0.3	2.80	20	125	<5	0.40	<1	14	23	38	3.06	<10	0.63	1050	<1	0.06	13	900	14	<5	<20	32	0.12	<10	79	<10	9	83
73	L33N 6300E	<5	0.3	2.74	15	95	<5	0.17	<1	11	32	30	3.47	<10	0.49	555	<1	0.07	13	1290	8	<5	<20	13	0.15	<10	87	<10	7	78
74	L33N 6325E	<5	0.5	2.48	20	125	<5	0.25	<1	12	36	41	3.57	<10	0.82	402	<1	0.07	17	760	12	<5	<20	27	0.17	<10	102	<10	7	68
75	L33N 6350E	5	0.9	2.54	20	90	<5	0.31	<1	14	22	56	3.35	<10	0.46	385	<1	0.02	13	450	6	<5	<20	22	0.13	<10	82	<10	29	46
76	L33N 6375E	5	0.5	3.37	30	130	5	0.19	<1	16	31	41	3.93	<10	0.73	494	<1	0.02	19	560	6	<5	<20	16	0.17	<10	112	<10	11	97
77	L34N 5900E	5	0.2	3.47	90	120	<5	0.80	<1	21	47	67	5.02	<10	1.36	636	<1	0.04	30	450	<2	<5	<20	49	0.18	<10	161	<10	17	109
78	L34N 5925E	<5	0.2	2.23	55	125	5	0.38	<1	14	30	40	4.95	<10	0.72	349	<1	0.02	21	690	12	<5	<20	29	0.19	<10	157	<10	7	98
79	L34N 5950E	5	0.4	2.73	35	170	<5	0.75	2	21	31	138	4.70	<10	0.98	1995	<1	0.02	26	580	14	<5	<20	44	0.20	<10	147	<10	14	157
80	L34N 5975E	<5	0.5	3.22	35	100	<5	0.31	<1	13	33	53	3.96	<10	0.79	305	<1	0.03	22	400	<2	<5	<20	23	0.18	<10	111	<10	11	86
81	L34N 6000E	5	0.2	1.96	20	130	<5	0.21	<1	13	23	27	3.75	<10	0.60	1489	<1	0.02	12	490	6	<5	<20	18	0.21	<10	111	<10	11	72
82	L34N 6025E	5	0.6	3.10	35	125	5	0.19	<1	18	43	43	5.05	<10	1.01	686	<1	0.02	23	1750	6	<5	<20	21	0.17	<10	165	<10	7	136
83	L34N 6050E	<5	0.4	2.52	50	160	5	0.19	1	14	41	40	4.64	<10	0.81	442	<1	0.02	21	380	12	<5	<20	17	0.21	<10	160	<10	11	88
84	L34N 6075E	5	0.5	3.57	25	125	<5	0.15	<1	14	32	40	3.80	<10	0.62	418	<1	0.02	17	560	6	<5	<20	15	0.18	<10	110	<10	11	85
85	L34N 6100E	10	0.6	3.44	40	150	<5	0.24	<1	19	59	87	6.00	<10	1.23	517	<1	0.02	34	1240	6	<5	<20	30	0.20	<10	155	<10	6	128
86	L34N 6125E	5	0.4	2.85	10	165	5	0.25	<1	21	39	49	5.84	<10	1.43	1226	<1	0.03	17	480	12	<5	<20	38	0.28	<10	239	<10	13	95
87	L34N 6150E	5	0.8	3.63	35	110	<5	0.21	<1	17	27	37	5.10	<10	0.83	295	<1	0.03	16	360	<2	<5	<20	20	0.25	<10	139	<10	15	68
88	L34N 6175E	5	0.2	1.82	5	180	5	0.47	<1	11	19	21	4.48	<10	0.50	601	<1	0.02	8	350	12	<5	<20	48	0.24	<10	136	<10	9	120
89	L34N 6200E	5	0.4	1.86	25	60	<5	0.11	<1	5	10	14	2.41	<10	0.12	69	<1	0.02	5	310	12	<5	<20	9	0.16	<10	61	<10	9	26
90	L34N 6225E	<5	0.3	2.84	10	60	<5	0.09	<1	6	9	13	2.16	<10	0.10	254	<1	0.02	4	1030	8	<5	<20	7	0.13	<10	48	<10	6	36
91	L34N 6250E	5	0.2	4.20	20	60	<5	0.08	<1	5	12	19	2.43	<10	0.11	358	<1	0.06	5	1330	6	<5	<20	4	0.12	<10	47	<10	9	39
92	L34N 6275E	5	0.4	3.25	25	130	<5	0.18	<1	16	25	34	3.84	<10	0.56	367	<1	0.07	13	740	8	<5	<20	17	0.16	<10	97	<10	11	89
93	L34N 6300E	5	0.3	2.46	15	105	<5	0.28	<1	9	17	20	2.77	<10	0.29	696	<1	0.06	6	880	14	<5	<20	16	0.14	<10	75	<10	9	56
94	L34N 6350E	5	0.2	2.22	15	140	<5	0.31	<1	15	40	36	3.66	<10	0.94	1733	<1	0.06	17	1540	8	<5	<20	25	0.16	<10	112	<10	8	86
95	L34N 6375E	5	0.8	2.69	20	105	<5	0.23	1	14	29	43	3.69	<10	0.74	822	<1	0.06	17	660	8	<5	<20	23	0.17	<10	105	<10	17	109
96	L34N 6400E	5	0.8	3.14	25	130	<5	0.23	1	13	28	56	3.65	<10	0.66	280	<1	0.06	17	430	4	<5	<20	27	0.16	<10	110	<10	27	75
97	L34N 6425E	5	1.3	2.09	25	100	5	0.06	1	9	13	22	3.22	<10	0.24	725	2	0.05	10	1270	20	<5	<20	5	0.07	<10	52	<10	2	99
98	L34N 6450E	5	0.4	2.21	30	90	5	0.18	<1	7	20	31	3.17	<10	0.37	361	<1	0.05	8	1190	14	<5	<20	15	0.12	<10	66	<10	5	58
99	L34N 6475E	<5	0.4	3.69	20	80	<5	0.15	<1	9	21	22	3.41	<10	0.37	303	<1	0.05	10	820	12	<5	<20	17	0.15	<10	82	<10	7	62
100	L34N 6500E	5	0.6	2.50	15	90	<5	0.45	<1	14	22	38	4.17	<10	0.93	542	<1	0.05	11	800	14	<5	<20	77	0.13	<10	101	<10	8	66
101	L34N 6525E	5	0.4	3.28	15	125	<5	0.50	<1	17	38	66	3.97	<10	1.14	828	<1	0.03	18	610	<2	<5	<20	45	0.15	<10	132	<10	12	85
102	L34N 6550E	30	0.3	2.09	35	195	<5	0.63	<1	14	26	31	3.62	<10	0.76	2547	<1	0.06	10	1330	8	<5	<20	60	0.12	<10	97	<10	8	77
103	L34N 6575E	10	0.2	2.60	35	70	5	0.14	<1	10	20	24	3.02	<10	0.38	264	<1	0.02	11	1120	8	<5	<20	14	0.14	<10	74	<10	7	54
104	L34N 6600E	5	0.4	1.89	15	125	5	0.47	<1	14	21	38	3.62	<10	0.41	652	<1	0.03	11	450	14	<5	<20	33	0.15	<10	102	<10	17	40
105	L34N 6625E	5	0.3	2.68	25	80	<5	0.17	<1	12	18	30	3.11	<10	0.33	802	<1	0.07	9	1070	8	<5	<20	13	0.12	<10	76	<10	9	59
106	L34N 6650E	<5	<0.2	1.74	15	80	<5	0.21	<1	10	20	24	3.14	<10	0.32	607	<1	0.02	11	780	8	<5	<20	17	0.11	<10	73	<10	4	52
107	L34N 6675E	5	0.3	2.93	60	50	<5	0.13	<1	14	17	39	3.15	<10	0.31	425	<1	0.02	10	1090	14	<5	<20	12	0.14	<10	71	<10	6	56
108	L34N 6700E	5	0.3	1.99	40	50	<5	0.08	<1	7	13	20	2.53	<10	0.18	294	<1	0.02	8	1300	10	<5	<20	7	0.11	<10	58	<10	3	39
109	L34N 6725E	5	0.3	2.15	75	60	<5	0.19	<1	11	19	32	3.32	<10	0.23	248	<1	0.02	9	460	12	<5	<20	17	0.14	<10	82	<10	5	42
110	L34N 6750E	5	0.6	2.89	95	60	<5	0.28	<1	16	23	45	4.07	<10	0.36	395	<1	0.02	14	1040	16	<5	<20	23	0.13	<10	94	<10	5	68

ECO TECH LABORATORY LTD.

ICP CERTIFICATE OF ANALYSIS AK 2005-677

COLUMBIA YUKON EXPLORATIONS INC.

Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
111	L34N 6775E	5	0.3	2.95	30	65	<5	0.67	<1	15	22	45	3.07	<10	0.42	1253	<1	0.02	15	1220	14	<5	<20	61	0.10	<10	84	<10	5	66
112	L34N 6800E	5	0.4	2.36	30	55	<5	0.10	<1	8	12	33	2.34	<10	0.21	408	<1	0.02	7	860	14	<5	<20	9	0.10	<10	59	<10	5	38
113	L34N 6825E	5	<0.2	3.20	30	60	<5	0.23	<1	10	11	32	2.61	<10	0.22	585	<1	0.02	8	1540	12	<5	<20	21	0.09	<10	62	<10	5	50
114	L34N 6850E	65	<0.2	3.21	100	80	<5	0.33	<1	17	20	42	3.02	<10	0.39	866	<1	0.02	16	1160	14	<5	<20	24	0.11	<10	76	<10	6	71
115	L34N 6875E	30	0.2	2.68	95	45	<5	0.19	<1	13	22	44	3.12	<10	0.42	326	<1	0.02	14	910	10	<5	<20	13	0.12	<10	88	<10	12	57
116	L35N 5900E	5	0.4	3.76	40	115	<5	1.09	1	14	70	80	3.89	<10	0.84	1747	<1	0.03	35	2500	6	<5	<20	97	0.11	<10	146	<10	23	95
117	L35N 5925E	5	0.3	2.95	25	150	<5	0.55	2	22	44	65	4.77	<10	1.13	1551	<1	0.05	32	680	8	<5	<20	44	0.19	<10	161	<10	14	137
118	L35N 5950E	10	1.3	2.95	30	75	<5	0.54	3	19	34	122	3.81	<10	0.72	1664	2	0.03	44	820	10	<5	<20	35	0.09	<10	117	<10	33	150
119	L35N 5975E	5	0.2	2.16	25	200	<5	0.26	<1	13	37	51	4.32	<10	0.88	353	<1	0.03	15	500	8	<5	<20	24	0.19	<10	157	<10	6	82
120	L35N 6000E	5	<0.2	2.75	35	160	<5	0.37	<1	17	53	65	4.81	<10	1.20	648	<1	0.04	30	450	10	<5	<20	34	0.22	<10	177	<10	9	102
121	L35N 6025E	5	0.4	2.78	40	135	5	0.20	<1	14	28	36	4.65	<10	0.62	354	<1	0.02	16	420	6	<5	<20	14	0.21	<10	123	<10	8	111
122	L35N 6050E	5	0.5	3.08	105	95	<5	0.71	<1	18	46	51	4.89	<10	0.90	484	<1	0.03	31	470	10	<5	<20	34	0.18	<10	146	<10	10	108
123	L35N 6075E	5	0.2	2.40	25	130	<5	0.42	<1	14	26	53	4.89	<10	0.88	336	<1	0.03	13	500	10	<5	<20	32	0.22	<10	167	<10	6	74
124	L35N 6100E	5	0.3	2.71	25	120	5	0.29	<1	16	53	42	5.55	<10	1.10	643	<1	0.03	21	880	12	<5	<20	18	0.20	<10	188	<10	8	127
125	L35N 6125E	10	0.3	2.53	70	115	<5	0.76	<1	17	34	42	4.27	<10	0.81	541	<1	0.03	26	860	8	<5	<20	41	0.15	<10	126	<10	6	174
126	L35N 6175E	5	0.2	3.29	30	165	<5	0.26	<1	19	45	58	4.60	<10	0.94	802	<1	0.03	28	1240	12	<5	<20	20	0.16	<10	159	<10	8	110
127	L35N 6200E	10	0.4	3.38	35	110	<5	0.19	<1	16	39	51	4.48	<10	0.83	510	<1	0.02	21	890	12	<5	<20	17	0.16	<10	144	<10	7	131
128	L35N 6225E	5	0.9	2.57	30	100	<5	0.12	<1	11	23	27	3.86	<10	0.41	338	<1	0.02	16	1480	14	<5	<20	9	0.12	<10	87	<10	3	129
129	L35N 6250E	45	0.4	2.49	75	175	<5	0.27	<1	17	36	41	6.23	<10	0.85	483	<1	0.02	16	580	16	<5	<20	107	0.20	<10	214	<10	5	108
130	L35N 6275E	15	0.8	1.88	130	100	<5	0.19	<1	10	22	50	4.26	<10	0.36	263	6	<0.01	22	350	16	<5	<20	13	0.04	<10	71	<10	5	124
131	L35N 6300E	5	0.4	3.13	60	65	<5	0.14	<1	10	16	32	3.02	<10	0.28	307	<1	0.02	8	1770	14	<5	<20	20	0.12	<10	68	<10	6	67
132	L35N 6325E	5	0.3	2.22	45	100	<5	0.13	<1	8	18	19	3.43	<10	0.19	551	<1	0.01	9	1290	18	<5	<20	8	0.14	<10	75	<10	3	72
133	L35N 6350E	5	0.4	1.32	20	70	<5	0.09	<1	6	13	33	3.05	<10	0.12	122	<1	0.01	8	490	14	<5	<20	7	0.10	<10	62	<10	<1	67
134	L35N 6375E	15	0.6	2.17	45	85	<5	0.10	<1	8	21	27	3.76	<10	0.22	138	<1	0.01	12	370	12	<5	<20	9	0.12	<10	83	<10	3	85
135	L35N 6400E	10	0.9	1.63	40	100	<5	0.08	1	11	17	26	3.72	<10	0.29	329	3	<0.01	16	550	18	<5	<20	6	0.05	<10	60	<10	<1	152
136	L35N 6425E	10	0.6	1.84	50	70	<5	0.06	<1	8	14	21	3.43	<10	0.18	318	2	0.01	12	940	16	<5	<20	3	0.07	<10	54	<10	<1	93
137	L35N 6450E	5	0.9	1.59	30	100	<5	0.05	1	10	16	19	3.73	<10	0.21	952	3	<0.01	11	1180	16	<5	<20	4	0.07	<10	59	<10	<1	122
138	L35N 6475E	15	0.3	2.64	60	100	<5	0.17	<1	11	22	27	3.28	<10	0.37	384	<1	0.02	15	1040	10	<5	<20	26	0.11	<10	84	<10	5	77
139	L35N 6500E	15	0.3	2.46	70	50	<5	0.36	<1	13	22	32	2.94	<10	0.42	400	<1	0.02	16	890	10	<5	<20	25	0.13	<10	78	<10	6	58
140	L35N 6525E	25	0.2	2.27	50	70	<5	0.21	<1	13	19	24	3.01	<10	0.31	539	<1	0.02	12	1030	12	<5	<20	14	0.13	<10	72	<10	3	59
141	L35N 6550E	5	0.4	2.55	50	60	<5	0.31	<1	13	25	35	3.84	<10	0.43	292	1	0.02	18	470	8	<5	<20	24	0.15	<10	98	<10	6	63
142	L35N 6575E	35	0.4	2.57	240	50	<5	0.18	<1	12	17	28	3.31	<10	0.21	216	<1	0.02	14	620	10	<5	<20	12	0.12	<10	61	<10	4	72
143	L35N 6600E	5	0.8	1.37	120	105	<5	0.42	<1	9	21	36	4.18	<10	0.35	226	<1	0.02	14	480	8	<5	<20	36	0.11	<10	112	<10	<1	78
144	L35N 6625E	5	0.5	2.68	30	65	<5	0.17	<1	11	27	35	3.17	<10	0.33	262	<1	0.02	20	1340	14	<5	<20	16	0.13	<10	77	<10	4	75
145	L35N 6650E	5	0.6	3.41	60	35	<5	0.15	<1	8	14	29	2.67	<10	0.18	118	<1	0.01	11	1330	14	<5	<20	11	0.13	<10	52	<10	4	52
146	L35N 6675E	5	0.5	2.13	130	65	<5	0.39	<1	13	30	103	3.37	<10	0.44	293	<1	0.02	30	710	10	<5	<20	30	0.11	<10	98	<10	7	106
147	L35N 6700E	5	0.5	1.64	60	90	<5	0.11	<1	11	18	29	3.83	<10	0.29	297	4	0.01	16	500	18	<5	<20	8	0.07	<10	63	<10	<1	165
148	L35N 6725E	35	0.5	2.38	305	100	<5	0.24	<1	19	23	47	3.60	<10	0.40	700	<1	0.01	19	980	14	<5	<20	20	0.14	<10	90	<10	5	100
149	L35N 6750E	300	2.8	2.97	365	60	<5	0.62	<1	14	25	53	3.53	<10	0.47	503	<1	0.01	15	1580	10	<5	<20	49	0.12	<10	99	<10	6	99
150	L35N 6775E	15	0.3	2.71	105	70	<5	0.42	<1	16	26	42	3.41	<10	0.44	489	<1	0.01	17	750	12	<5	<20	33	0.13	<10	97	<10	4	91

22-Jul-05

ECO TECH LABORATORY LTD.

ICP CERTIFICATE OF ANALYSIS AK 2005-677

COLUMBIA YUKON EXPLORATIONS INC.

Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
151	L35N 6800E	5	0.4	2.42	45	115	<5	0.36	<1	14	19	28	3.14	<10	0.35	859	<1	0.01	13	960	12	<5	<20	22	0.15	<10	82	<10	5	92
152	L35N 6825E	35	0.4	2.09	190	90	<5	0.29	<1	16	19	31	3.59	<10	0.32	685	<1	0.02	14	620	26	<5	<20	21	0.14	<10	87	<10	7	103
153	L35N 6850E	15	1.0	2.70	490	90	<5	0.69	<1	23	27	134	4.03	20	0.59	2256	2	0.03	29	850	12	<5	<20	40	0.13	<10	105	<10	57	111
154	L35N 6875E	25	0.8	1.75	385	90	<5	0.57	<1	19	26	70	4.25	<10	0.72	1691	2	0.02	23	580	10	<5	<20	25	0.15	<10	108	<10	19	130

QC DATA:Repeat:

1	HR 1	0.5	2.42	40	110	<5	0.16	<1	8	15	26	2.81	<10	0.20	865	1	0.02	10	1050	22	<5	<20	9	0.08	<10	58	<10	4	81	
3	HR 3	155																												
5	HR 6	120																												
10	HR 11	30	0.6	4.16	55	65	<5	0.80	<1	19	23	68	4.26	<10	0.25	358	2	0.02	33	1260	6	<5	<20	69	0.10	<10	88	<10	13	64
19	HR 21	10	0.3	3.77	50	85	<5	0.27	<1	10	23	37	2.86	<10	0.36	266	<1	0.05	18	810	14	<5	<20	27	0.11	<10	81	<10	9	80
22	HR 24	25																												
24	HR 26	5																												
28	HR 30	10	0.6	3.92	60	65	<5	0.75	<1	20	31	76	4.04	<10	0.65	642	<1	0.06	35	740	10	<5	<20	36	0.15	<10	107	<10	20	134
35	HR 37	25																												
36	HR 38	10	0.3	3.17	35	95	<5	0.23	<1	20	31	88	4.36	<10	0.74	512	<1	0.02	32	850	8	<5	<20	14	0.13	<10	104	<10	11	93
45	L32N 6100E	10	0.2	2.15	20	100	<5	0.11	<1	12	19	27	3.50	<10	0.31	729	<1	0.05	10	1270	12	<5	<20	10	0.15	<10	82	<10	5	104
52	L32N 6275E	55																												
54	L32N 6325E	50	0.3	2.61	30	205	5	0.47	<1	13	27	36	3.59	<10	0.62	714	<1	0.02	19	1010	14	<5	<20	26	0.13	<10	88	<10	5	120
63	L33N 6050E	5	1.4	3.24	25	70	5	0.27	1	17	32	56	4.43	<10	0.91	609	1	0.02	22	1160	6	<5	<20	19	0.14	<10	117	<10	8	87
71	L33N 6250E	<5	0.2	2.59	15	95	<5	0.23	<1	10	19	30	2.32	<10	0.41	275	<1	0.06	11	660	8	<5	<20	15	0.14	<10	67	<10	8	55
80	L34N 5975E	<5	0.5	3.24	40	100	<5	0.32	<1	14	33	53	3.99	<10	0.78	311	<1	0.03	22	410	<2	<5	<20	25	0.19	<10	112	<10	11	87
89	L34N 6200E	5	0.4	1.88	25	60	<5	0.11	<1	6	10	14	2.44	<10	0.12	73	<1	0.02	4	310	8	<5	<20	9	0.17	<10	62	<10	9	27
98	L34N 6450E	5	0.4	2.23	30	90	5	0.18	<1	7	20	31	3.18	<10	0.36	369	<1	0.07	8	1210	12	<5	<20	14	0.12	<10	66	<10	6	59
106	L34N 6650E	5	<0.2	1.82	20	75	<5	0.22	<1	10	21	25	3.25	<10	0.34	592	<1	0.02	11	830	10	<5	<20	15	0.12	<10	75	<10	2	55
115	L34N 6875E	30	0.2	2.64	95	45	<5	0.19	<1	13	20	44	3.04	<10	0.38	321	<1	0.02	13	950	12	<5	<20	13	0.12	<10	84	<10	12	56
124	L35N 6100E	5	0.3	2.67	25	120	<5	0.30	<1	17	52	43	5.58	<10	1.07	650	<1	0.03	22	880	12	<5	<20	20	0.21	<10	187	<10	8	127
129	L35N 6250E	50																												
133	L35N 6350E	5	0.5	1.36	20	75	<5	0.10	<1	6	13	31	3.18	<10	0.12	137	<1	0.01	8	530	14	<5	<20	6	0.11	<10	66	<10	1	68
141	L35N 6550E	<5	0.5	2.39	50	55	<5	0.30	<1	13	22	33	3.72	<10	0.38	279	<1	0.02	15	490	10	<5	<20	20	0.15	<10	92	<10	7	60
142	L35N 6575E	30																												
148	L35N 6725E	60																												
149	L35N 6750E	165																												
152	L35N 6825E	30																												

22-Jul-05

ECO TECH LABORATORY LTD.

ICP CERTIFICATE OF ANALYSIS AK 2005-677

COLUMBIA YUKON EXPLORATIONS INC.

Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
Standard:																														
GEO '05		145	1.5	1.66	60	150	<5	1.37	<1	10	58	91	3.82	<10	0.85	573	<1	0.08	29	560	22	<5	<20	54	0.10	<10	72	<10	11	73
GEO '05		135	1.5	1.67	60	150	<5	1.34	<1	10	56	93	3.70	<10	0.87	564	<1	0.03	29	520	22	<5	<20	54	0.10	<10	75	<10	13	61
GEO '05		140	1.5	1.79	60	155	<5	1.40	<1	10	58	98	3.82	<10	0.92	573	<1	0.04	29	560	22	<5	<20	53	0.11	<10	72	<10	14	60
GEO '05		140	1.5	1.42	65	140	<5	1.30	<1	10	55	83	3.69	<10	0.71	557	<1	0.03	29	590	22	<5	<20	58	0.10	<10	72	<10	9	69
GEO '05		130	1.5	1.39	65	145	<5	1.32	<1	10	56	81	3.73	<10	0.71	563	<1	0.03	29	600	22	<5	<20	57	0.10	<10	72	<10	10	71
GEO '05		145																												

24-Aug-05

ECO TECH LABORATORY LTD.
 10041 Dallas Drive
KAMLOOPS, B.C.
 V2C 6T4

Phone: 250-573-5700
 Fax : 250-573-4557

ICP CERTIFICATE OF ANALYSIS AK 2005-895

COLUMBIA YUKON EXPLORATIONS INC.
 5936 Stafford Road
Nelson, BC
 V1L 6P3

ATTENTION: Bernie Augsten / Gillian Feyer

No. of samples received: 71
 Sample type: Soil

Project #: Barnes Creek**Shipment #: n/a**Samples submitted by: *Bernie Augsten***Values in ppm unless otherwise reported**

Et #.	Tag #	Au(ppb)	Aq	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
1	L25N 5950E	10	0.9	1.50	85	100	<5	0.12	<1	9	17	35	3.30	<10	0.29	460	5	0.04	16	1120	4	<5	<20	12	0.05	<10	58	<10	3	103
2	L25N 5975E	5	0.7	1.42	50	200	<5	0.17	<1	7	14	17	2.97	<10	0.18	2154	3	0.05	11	3230	8	<5	<20	17	0.04	<10	50	<10	<1	97
3	L25N 6000E	10	0.6	2.10	65	80	<5	0.06	<1	9	15	25	3.04	<10	0.20	491	2	0.04	11	1410	2	<5	<20	6	0.06	<10	51	<10	4	80
4	L25N 6025E	5	1.0	2.15	50	85	<5	0.06	<1	8	13	24	2.65	<10	0.16	421	2	0.05	9	1200	2	<5	<20	6	0.07	<10	47	<10	4	68
5	L25N 6050E	5	1.1	2.31	40	75	<5	0.05	<1	7	10	20	2.29	<10	0.11	457	1	0.04	8	1110	2	<5	<20	7	0.06	<10	40	<10	6	59
6	L25N 6075E	5	0.6	2.48	30	45	<5	0.04	<1	5	6	15	1.53	<10	0.04	352	<1	0.04	5	1730	2	<5	<20	3	0.06	<10	25	<10	6	30
7	L25N 6100E	5	1.8	2.53	35	65	<5	0.05	<1	5	8	19	1.50	<10	0.10	208	<1	0.05	7	1150	2	<5	<20	4	0.06	<10	34	<10	8	51
8	L25N 6125E	10	1.5	2.15	40	60	<5	0.08	<1	7	12	20	2.10	<10	0.16	301	2	0.04	8	1600	<2	<5	<20	6	0.05	<10	44	<10	4	64
9	L25N 6150E	5	0.6	1.86	55	50	<5	0.04	<1	9	12	17	2.49	<10	0.15	913	2	0.04	8	2150	16	<5	<20	3	0.06	<10	47	<10	2	61
10	L25N 6175E	5	0.5	2.48	15	50	<5	0.10	<1	7	17	27	1.76	<10	0.16	155	<1	0.02	9	960	<2	<5	<20	9	0.08	<10	49	<10	8	37
11	L25N 6200E	5	0.6	3.20	25	30	<5	0.05	<1	5	5	15	1.19	<10	0.04	189	<1	0.05	3	1000	<2	<5	<20	3	0.07	<10	25	<10	10	26
12	L25N 6225E	5	0.7	2.18	30	50	<5	0.06	<1	3	7	15	1.39	<10	0.07	47	1	0.04	6	780	2	<5	<20	5	0.04	<10	31	<10	6	32
13	L25N 6250E	5	0.3	2.50	35	65	<5	0.13	<1	7	16	32	1.71	<10	0.30	144	<1	0.01	15	720	4	<5	<20	10	0.07	<10	55	<10	9	81
14	L25N 6275E	5	0.5	2.52	20	70	<5	0.12	<1	8	22	36	2.85	<10	0.30	175	<1	0.02	14	930	<2	<5	<20	13	0.09	<10	73	<10	6	64
15	L25N 6300E	5	0.4	2.52	25	90	<5	0.16	<1	12	35	49	3.23	<10	0.47	518	<1	0.06	45	1330	<2	<5	<20	17	0.08	<10	82	<10	4	71
16	L25N 6325E	10	0.6	2.79	30	95	<5	0.14	<1	9	29	49	3.42	<10	0.45	236	<1	0.05	24	880	<2	<5	<20	16	0.10	<10	91	<10	6	89
17	L25N 6350E	5	0.4	2.81	35	75	<5	0.36	<1	14	20	60	3.34	<10	0.43	612	1	0.05	24	890	<2	<5	<20	21	0.07	<10	68	<10	12	118
18	L25N 6375E	5	0.7	3.18	45	105	<5	1.00	<1	16	19	150	3.07	<10	0.42	2272	2	0.06	32	1390	<2	<5	<20	40	0.05	<10	72	<10	22	153
19	L25N 6400E	5	0.4	2.77	45	80	<5	0.12	<1	12	15	37	2.89	<10	0.28	495	1	0.05	15	970	<2	<5	<20	8	0.08	<10	55	<10	10	100
20	L25N 6425E	5	0.9	2.68	35	70	<5	0.62	<1	6	10	22	2.04	<10	0.17	270	<1	0.02	8	2080	<2	<5	<20	19	0.08	<10	39	<10	8	69
21	L25N 6450E	5	0.8	1.53	30	90	<5	0.23	<1	6	12	15	2.73	<10	0.19	553	2	0.01	7	1910	4	<5	<20	9	0.05	<10	48	<10	1	54
22	L25N 6475E	5	1.0	1.68	30	160	<5	0.10	<1	8	13	17	2.75	<10	0.20	699	2	<0.01	10	2080	4	<5	<20	7	0.06	<10	46	<10	2	74
23	L25N 6500E	5	0.9	3.09	140	50	<5	1.40	<1	8	14	117	1.93	<10	0.26	265	1	0.09	24	1460	<2	<5	<20	48	0.04	<10	38	<10	16	117
24	L25N 6525E	5	0.6	2.91	25	60	<5	0.25	<1	10	20	39	3.06	<10	0.34	274	<1	0.05	13	1130	<2	<5	<20	15	0.11	<10	84	<10	7	62
25	L25N 6550E	5	0.2	2.53	20	60	<5	0.17	<1	10	18	41	3.17	<10	0.39	285	<1	0.05	10	740	<2	<5	<20	14	0.12	<10	87	<10	9	63
26	L25N 6575E	5	0.7	2.58	45	90	<5	1.21	2	18	41	112	4.03	<10	0.82	920	<1	0.07	34	720	<2	<5	<20	53	0.09	<10	123	<10	17	127
27	L25N 6600E	5	1.0	3.48	90	90	<5	1.03	2	21	37	172	4.06	<10	0.66	1075	<1	0.07	45	930	<2	<5	<20	45	0.09	<10	109	<10	27	149
28	L25N 6625E	5	0.6	3.60	130	40	<5	0.92	<1	9	11	53	2.07	<10	0.19	297	<1	0.06	16	1040	<2	<5	<20	34	0.10	<10	39	<10	19	96
29	L25N 6650E	10	0.3	3.00	50	65	<5	0.26	<1	13	23	27	4.10	<10	0.47	359	<1	0.06	15	1240	<2	15	<20	21	0.12	<10	106	<10	7	87
30	L25N 6675E	10	0.6	3.28	70	120	<5	1.30	1	18	32	138	3.75	<10	0.66	2676	2	0.08	39	1130	<2	<5	<20	53	0.09	<10	107	<10	19	142

24-Aug-05

ECO TECH LABORATORY LTD.

ICP CERTIFICATE OF ANALYSIS AK 2005-895

Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
31	L25N 6700E	35	0.4	2.52	85	80	<5	0.29	<1	13	20	42	3.32	<10	0.25	823	<1	0.02	16	1430	<2	<5	<20	17	0.09	<10	81	<10	7	112
32	L25N 6725E	10	0.4	2.99	60	85	<5	0.39	<1	20	36	84	4.24	<10	0.78	924	2	0.06	32	1050	<2	10	<20	30	0.10	<10	125	<10	13	113
33	L25N 6750E	10	0.2	2.43	50	135	<5	0.31	<1	18	31	60	4.29	<10	0.65	1199	3	0.02	31	1080	<2	<5	<20	20	0.09	<10	119	<10	7	124
34	L25N 6775E	20	0.6	2.32	130	80	<5	0.87	<1	24	48	141	5.05	<10	1.01	994	2	0.04	44	920	<2	<5	<20	51	0.08	<10	143	<10	16	111
35	L26N 5950E	10	0.7	2.46	60	60	<5	0.05	<1	6	14	24	2.69	<10	0.16	295	3	<0.01	9	1540	<2	<5	<20	5	0.06	<10	47	<10	3	70
36	L26N 5975E	5	0.7	2.14	30	75	<5	0.07	<1	5	10	15	2.08	<10	0.11	368	<1	0.04	6	1450	<2	<5	<20	7	0.06	<10	42	<10	3	44
37	L26N 6000E	35	0.6	2.56	60	85	<5	0.10	<1	11	16	38	3.19	<10	0.29	555	1	0.05	12	1660	<2	<5	<20	12	0.08	<10	67	<10	6	77
38	L26N 6025E	25	0.4	2.40	60	65	<5	0.18	<1	12	13	32	2.91	<10	0.24	643	<1	0.05	10	2070	<2	<5	<20	12	0.09	<10	57	<10	5	66
39	L26N 6050E	115	0.9	2.57	245	60	<5	0.86	<1	12	23	71	3.39	<10	0.43	1767	3	0.05	18	1140	<2	<5	<20	33	0.06	<10	94	<10	11	76
40	L26N 6075E	45	0.4	2.10	60	100	<5	0.16	<1	15	25	48	3.52	<10	0.39	899	2	0.05	19	2010	4	<5	<20	14	0.07	<10	90	<10	2	93
41	L36N 6400E	5 <0.2	1.24	25	110		<5	0.12	<1	8	13	19	2.78	<10	0.24	928	3	0.04	10	990	12	<5	<20	7	0.05	<10	46	<10	1	95
42	L36N 6425E	10	0.5	1.12	55	215	<5	0.20	1	12	16	30	3.87	<10	0.32	2626	4	0.04	18	1420	26	<5	<20	12	0.04	<10	46	<10	<1	188
43	L36N 6450E	10	0.7	1.89	80	65	<5	0.08	<1	7	9	22	2.49	<10	0.17	425	1	0.05	10	1530	6	<5	<20	5	0.06	<10	36	<10	5	92
44	L36N 6475E	30	1.5	2.01	445	55	<5	0.98	<1	14	24	154	3.26	20	0.45	1166	4	0.05	26	1040	4	<5	<20	45	0.04	<10	75	<10	58	117
45	L36N 6500E	10	1.1	1.41	200	50	<5	0.21	<1	9	22	58	3.27	<10	0.28	121	<1	0.05	12	400	8	<5	<20	17	0.13	<10	70	<10	11	55
46	L36N 6525E	35	0.4	2.22	210	60	<5	0.33	<1	14	22	44	3.27	<10	0.45	485	1	0.06	12	470	<2	<5	<20	26	0.13	<10	82	<10	12	79
47	L36N 6550E	30 <0.2	1.70	105	55		<5	0.25	<1	11	31	27	3.44	<10	0.47	270	<1	0.05	11	580	<2	<5	<20	22	0.13	<10	106	<10	7	53
48	L36N 6575E	350	0.3	1.02	90	55	<5	0.15	<1	8	25	26	3.50	<10	0.33	134	<1	0.05	9	310	10	<5	<20	13	0.12	<10	101	<10	4	55
49	L36N 6600E	20	0.2	1.98	100	85	<5	0.62	<1	18	37	42	4.05	<10	0.60	561	<1	0.05	18	510	<2	<5	<20	41	0.15	<10	125	<10	10	72
50	L36N 6625E	15	0.2	2.41	75	75	<5	0.38	<1	13	18	33	3.96	<10	0.63	406	<1	0.05	9	1200	<2	<5	<20	39	0.12	<10	111	<10	8	77
51	L36N 6650E	25	0.3	2.55	205	65	<5	0.43	<1	15	17	37	3.92	<10	0.47	795	<1	0.05	10	680	<2	<5	<20	39	0.14	<10	103	<10	13	81
52	L36N 6675E	65	0.7	2.43	400	70	<5	0.22	<1	20	33	73	4.55	<10	0.70	343	4	0.05	20	620	<2	<5	<20	25	0.14	<10	120	<10	8	82
53	L36N 6700E	10	0.2	2.75	30	90	<5	0.30	<1	16	30	31	3.46	<10	0.45	328	<1	0.05	13	730	<2	<5	<20	33	0.16	<10	101	<10	10	85
54	L36N 6725E	225	0.5	2.67	140	90	<5	0.32	<1	17	37	39	4.37	<10	0.61	319	<1	0.05	19	430	<2	<5	<20	31	0.17	<10	129	<10	11	69
55	L36N 6750E	15	0.3	2.26	100	95	<5	0.31	<1	14	20	19	3.30	<10	0.45	358	<1	0.06	10	680	2	<5	<20	29	0.13	<10	99	<10	10	76
56	L36N 6775E	20	0.2	2.24	100	65	<5	0.37	<1	13	25	18	3.77	<10	0.57	340	<1	0.05	12	750	4	<5	<20	34	0.18	<10	118	<10	9	85
57	L36N 6800E	160	2.0	2.47	840	55	<5	0.95	<1	21	32	179	3.74	40	0.55	1617	1	0.05	22	730	8	10	<20	45	0.11	<10	99	<10	79	105
58	L36N 6825E	55	0.3	2.29	350	80	<5	0.27	<1	20	43	40	4.61	<10	0.75	590	<1	0.05	20	590	2	<5	<20	18	0.20	<10	144	<10	11	129
59	L36N 6850E	20	0.5	2.32	205	90	<5	0.27	<1	20	34	40	4.44	<10	0.60	961	<1	0.05	16	1130	<2	<5	<20	25	0.16	<10	133	<10	9	116
60	L36N 6875E	50	0.7	2.12	245	100	<5	0.18	<1	19	48	43	4.32	<10	0.79	682	<1	0.05	24	630	2	<5	<20	21	0.16	<10	130	<10	7	119
61	L37N 6600E	10	0.5	2.21	55	85	<5	0.34	<1	16	36	53	3.95	<10	0.72	606	<1	0.05	25	570	<2	<5	<20	27	0.11	<10	110	<10	8	104
62	L37N 6625E	30	0.3	2.65	45	135	<5	0.19	<1	19	36	46	4.09	<10	0.74	894	<1	0.06	28	1130	<2	<5	<20	20	0.12	<10	110	<10	7	140
63	L37N 6650E	185	0.4	2.59	120	85	<5	0.36	<1	20	33	55	3.90	<10	0.61	1115	<1	0.06	26	1010	2	<5	<20	30	0.09	<10	105	<10	8	108
64	L37N 6675E	40	0.4	2.78	75	85	<5	0.67	<1	18	32	58	3.77	<10	0.64	773	<1	0.06	26	730	<2	<5	<20	42	0.11	<10	111	<10	14	98
65	L37N 6700E	10	0.3	2.25	45	75	<5	0.84	1	19	35	73	3.97	<10	0.82	1071	2	0.07	29	690	<2	<5	<20	47	0.08	<10	119	<10	13	112
66	L37N 6725E	15	0.3	1.85	40	115	<5	0.57	1	16	32	56	3.38	<10	0.58	809	1	0.05	27	720	6	<5	<20	36	0.08	<10	98	<10	8	118
67	L37N 6750E	10	0.3	1.74	50	75	<5	0.49	<1	18	33	61	3.53	<10	0.44	810	<1	0.05	28	610	6	<5	<20	30	0.08	<10	100	<10	7	126
68	L37N 6775E	60	0.5	1.90	175	40	<5	1.20	<1	16	27	116	3.14	<10	0.49	808	2	0.05	27	910	<2	<5	<20	48	0.04	<10	83	<10	18	70
69	L37N 6800E	10	0.3	2.35	130	55	<5	0.40	<1	14	28	51	3.76	<10	0.38	318	1	0.05	23	480	<2	<5	<20	26	0.09	<10	100	<10	10	91
70	L37N 6825E	70	0.4	2.46	165	60	<5	0.68	<1	18	25	52	3.67	<10	0.45	845	2	0.06	22	710	4	<5	<20	32	0.07	<10	90	<10	8	73
71	L37N 6850E	20	0.3	2.29	145	65	<5	0.95	<1	14	21	44	3.50	<10	0.33	387	<1	0.06	17	460	<2	<5	<20	43	0.0					

24-Aug-05

ECO TECH LABORATORY LTD.

ICP CERTIFICATE OF ANALYSIS AK 2005-895

Et #.	Tag #	Au(ppb)	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
QC DATA:																														
Repeat:																														
1	L25N 5950E	10	0.8	1.47	85	95	<5	0.12	<1	9	18	34	3.44	<10	0.33	462	4	0.04	17	1100	6	<5	<20	11	0.05	<10	61	<10	2	111
10	L25N 6175E	5	0.5	2.49	20	50	<5	0.10	<1	7	16	27	1.71	<10	0.15	153	<1	0.05	9	940	<2	<5	<20	9	0.07	<10	48	<10	8	37
19	L25N 6400E	5	0.4	2.63	45	75	<5	0.12	<1	12	14	35	2.80	<10	0.26	482	<1	0.05	14	920	2	<5	<20	8	0.08	<10	52	<10	10	98
28	L25N 6625E	5	0.6	3.53	125	40	<5	0.90	<1	9	10	53	2.05	<10	0.19	302	<1	0.05	15	970	<2	<5	<20	33	0.10	<10	39	<10	18	93
36	L26N 5975E	5	0.7	1.97	30	65	<5	0.07	<1	4	9	14	1.94	<10	0.10	329	<1	0.04	6	1390	<2	<5	<20	6	0.06	<10	39	<10	3	43
39	L26N 6050E	90																												
45	L36N 6500E	1.1	1.39	200	50		<5	0.21	<1	9	21	58	3.28	<10	0.26	117	<1	0.06	12	400	10	<5	<20	18	0.12	<10	67	<10	11	56
46	L36N 6525E	30																												
48	L36N 6575E	100																												
54	L36N 6725E	120	0.5	2.53	130	90	<5	0.31	<1	17	38	36	4.24	<10	0.59	312	<1	0.06	17	420	2	<5	<20	30	0.16	<10	124	<10	10	69
57	L36N 6800E	130																												
63	L37N 6650E	215	0.5	2.57	125	80	<5	0.35	<1	20	31	55	3.75	<10	0.58	1083	<1	0.06	26	980	<2	<5	<20	30	0.08	<10	101	<10	7	104
71	L37N 6850E	15	0.3	2.24	135	65	<5	0.93	<1	14	21	44	3.46	<10	0.33	380	1	0.05	18	440	<2	<5	<20	43	0.09	<10	83	<10	7	54
Standard:																														
GEO '05		140	1.5	1.48	60	135	<5	1.26	<1	18	59	84	3.59	<10	0.93	546	<1	0.02	29	570	20	<5	<20	55	0.11	<10	70	<10	10	74
GEO '05		135	1.5	1.54	55	145	<5	1.29	<1	19	58	87	3.42	<10	0.87	528	<1	0.02	28	580	20	<5	<20	54	0.11	<10	71	<10	10	75
GEO '05		140	1.5	1.41	55	140	<5	1.22	<1	18	58	87	3.43	<10	0.76	530	<1	0.06	28	530	20	<5	<20	56	0.10	<10	72	<10	10	74
GEO '05		135																												

ECO TECH LABORATORY LTD.

Jutta Jealouse

B.C. Certified Assayer

JJ/ga

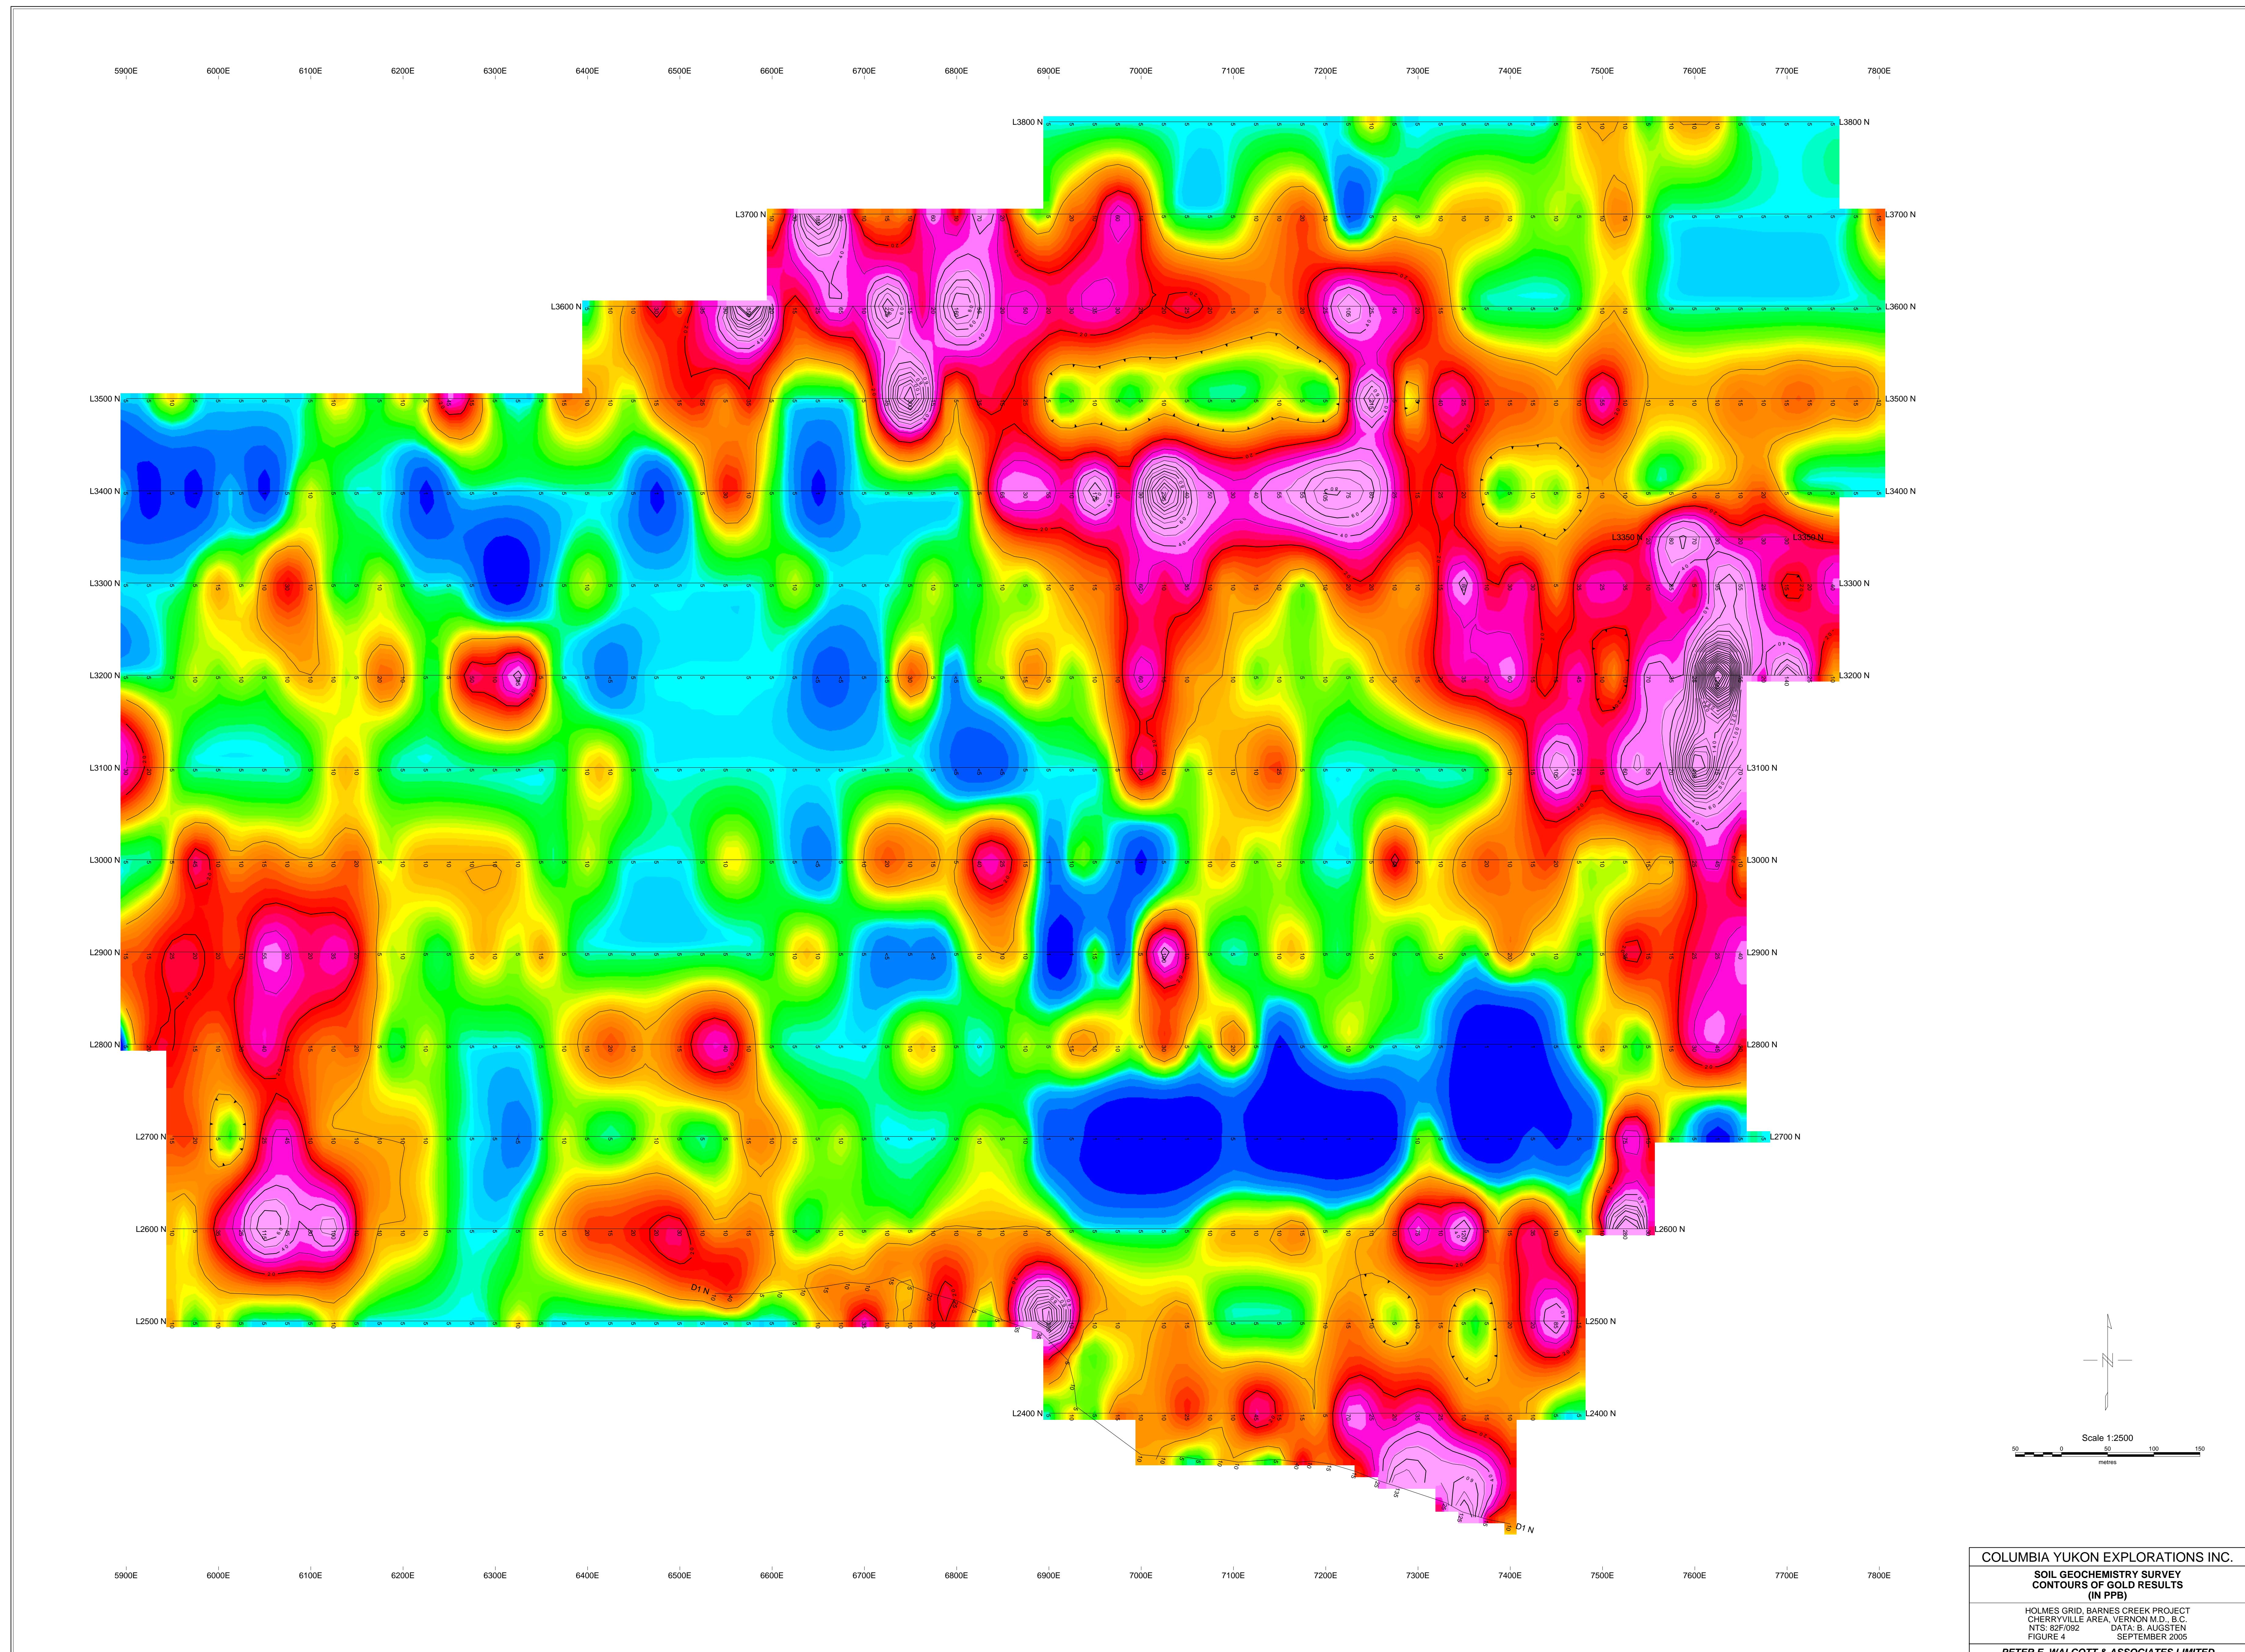


Table 2: ANALYTICAL STATISTICS

	GOLD	SILVER	ARSENIC
# of Samples	979	979	979
Mean	17.7	0.5	68
Minimum	1	0.1	1
Maximum	1230	8.9	850
Standard Deviation	51	0.4	106

This soil program was successful in discovering several multielement soil anomalies, particularly gold-silver-arsenic +/- antimony +/- copper.

GOLD:

The most significant gold anomaly occurs between Lines 3100N and 3700N, and between 6550E and 7700E describing an irregular northwest-trending feature open both to the northwest and southeast (see Figure 4). The anomaly is approximately 1200 metres by 300 metres with some significant areas of low values specifically on L3500N between 6900E and 7200E. Within the broader northwest-trending feature there are several areas that appear to represent north-trending structural features. The first of these is at 7600E to 7650E between L3100N and 3400N; the second at 7200E to 7250E between L3400N and 3600N; and the third area is at 6750E between L3500N and 3700N. Both the north and south contacts of the northwest-trending anomaly are fairly sharp indicating either a structural or lithological control to the gold mineralization.

In the southern part of the soil grid there is another northwest-trending anomaly parallel to the northern anomaly although more poorly defined. It is best described as a series of anomalous clusters of gold anomalies which together define the northwest trend. 365ppb gold in soil occurs at L2500N/6900E. Interestingly, visible gold was panned from this anomaly.

