

**Assessment Report on Diamond Drilling  
on the**



**Congress Property  
Lillooet Mining Division  
British Columbia  
Canada**

**N.T.S.: 092J/15W**

**UTM co-ord.: 514,000 m E., 5,638,000 m N.  
UTM Zone 10**

**Owner/Operator  
Levon Resources Ltd.  
Suite 400 – 455 Granville Street  
Vancouver, BC V6C 1T1**

**Author:  
Chris J. Sampson, P.Eng.  
2696 11<sup>th</sup> Avenue West  
Vancouver, BC V6K 2L6**

**May 5, 2007**

**GEOLOGICAL SURVEY BRANCH  
ASSESSMENT REPORT**

**29-13**

## Table of Contents

Summary	1
Property Description and Location	2
Accessibility, Climate, Local Resources, Infrastructure and Physiography	3
History	4
Geological Setting	5
Deposit Types	5
Mineralization	5
Other District Properties	6
2006 Diamond Drilling	6
Levon Congress Drill Results – 2006	7
Sample Preparation Analysis and Security	8
Conclusions and Recommendations	8
References	9
List of Figures	
	Follows Page:
Figure 1: General Location Map	1
Figure 2: Claim Location Map	2
Figure 3: Regional Geology	5
List of Maps	
Map 1: Overview Map	In Pocket
Cross Sections:-	In Pocket
Golden Ledge: GL-06-01, GL-06-02/03, GL-06-04/05	
Lou Zone: LZ-06-01, LZ-06-02, LZ-06-03, LZ-06-04, LZ-06-05, LZ-06-06, LZ-06-07, LZ-06-08, LZ-06-09	
Howard Zone: C-06-01, C-06-02	
List of Tables	
Table 1: List of Mineral Claims	2
Table 2: List of Mineralized Diamond Drill Hole Intersections	6
List of Appendices	
Appendix A: Statement of Costs	10
Appendix B: Diamond Drill Logs	11
Appendix C: Assay Results and Assay Procedure	12
Appendix D: Author's Statement of Qualification	13, 14

## 1. Summary

This report describes results of a diamond drilling programme done on the Congress Property in October/November 2006.

The Congress Property ("the property") is located on the north side of Carpenter Lake, 90 kilometres west of the town of Lillooet (Fig. 1 & 2). The property can be accessed by automobile from Lillooet by taking B.C. Highway 40 for 96 kilometres west to the property.

The property consists of one reverted crown granted mineral claim, 3 mineral leases and 11 mineral claims totaling 2,432.756 hectares (Fig. 2, Table 1) located on the north side of Carpenter Lake 4 kilometres northeast of Goldbridge in Lillooet Mining Division, NTS 092J15W. The property is owned by Levon Resources Ltd. ("the company") and Veronex Resources Ltd. The property is easily accessible by automobile on the Goldbridge to Lillooet Road, B.C. Highway 40, which crosses the southern part of the property. The Slim Creek forest access road, which turns off the highway on the property and crosses the property in a northwesterly direction, and numerous access trails and roads built on the property during previous exploration programs provide good access to the rest of the property (Map 1).

The property covers Mississippian to Middle Jurassic rocks of the Bridge River Complex, mainly submarine basalt and andesite with minor chert, argillite and mafic intrusives (Fig. 3). These rocks are cut by northwest trending regional scale structures, in some cases with contained Tertiary feldspar porphyry dacite dykes, sub-parallel with the Ferguson and Cadwallader Structures. The structures on the property are roughly the same distance from the Upper Cretaceous-Tertiary granitic Bendor Intrusions as the Bralorne/Pioneer mines. The Bendor Intrusions are a postulated source for the gold mineralization at the Bralorne mine.

The structures on the property are mineralized with gold and silver in quartz-carbonate veins and in altered vein selvages for up to 5 metres from the veins. These veins have received considerable past work, including 6 adits with more than 2,235 metres of underground workings (Map 1). The following resources have been developed:

	<b>Tonnes</b>	<b>Oz/ton</b>	<b>g/tonne</b>	<b>Mineral Resource Category</b>
Howard	273,402.5	0.264	8.2	inferred
Howard	25,909	0.367	11.4	Indicated
Howard	40,192	0.280	9.68	Measured
Lou underground	189,548	0.350	10.9	Inferred
Lou open pit	124,300	0.077	2.4	Inferred
Congress	106,678	0.238	7.4	Indicated



Levon Resources Ltd.			
CONGRESS PROJECT			
Lillooet M.D. British Columbia			
General Location Map			
Scale	as shown	UTM	NAD83 Zone 10
Date	April 2006	TRIM	92J.086,087,096,097
By	DSD/AGB	NTS	92J/15
			Fig <b>1</b>



These resources were outlined in the 1930's, 1950's, 1960's and 1980's but were not mined because of the refractory nature of the mineralization.

Numerous other showings including the Ozone, Gun, Slide, Paul and Golden Ledge exist on the property, mainly in the Gun Creek canyon. These are generally narrow structures with erratic orientations very disrupted by the major structures following the Gun Creek canyon.

## 2. Property Description and Location

The property consists of one reverted crown granted mineral claim, 3 mineral leases and 11 mineral claims totaling 109 cells covering approximately 2,432 hectares as listed in Table 1 below:

<b>Tenure #</b>	<b>Issue Date</b>	<b>Area in Ha</b>
228251	1979/Jan/23	25.00
228252	1979/Jan/23	25.00
228376	1980/Nov/28	100.00
228461	1982/Nov/10	25.00
228462	1982/Nov/10	25.00
228501	1983/Apr/11	100.00
228544	1983/Oct/19	150.00
228736	1985/Nov/14	25.00
228738	1985/Nov/14	25.00
351061	1996/Sep/30	25.00
509835	2005/Mar/30	326.11
509864	2005/Mar/30	438
510035	2005/Apr/01	17
510050	2005/Apr/01	438
510227	2005/Apr/05	1,826
510318	2005/Apr/07	365
510327	2005/Apr/07	2,287
510708	2005/Apr/13	365
511100	2005/Apr/19	1,826
517111	2005/July/12	2,723
517166	2005/July/12	2,723
517274	2005/July/12	2,723
517277	2005/July/12	2,723

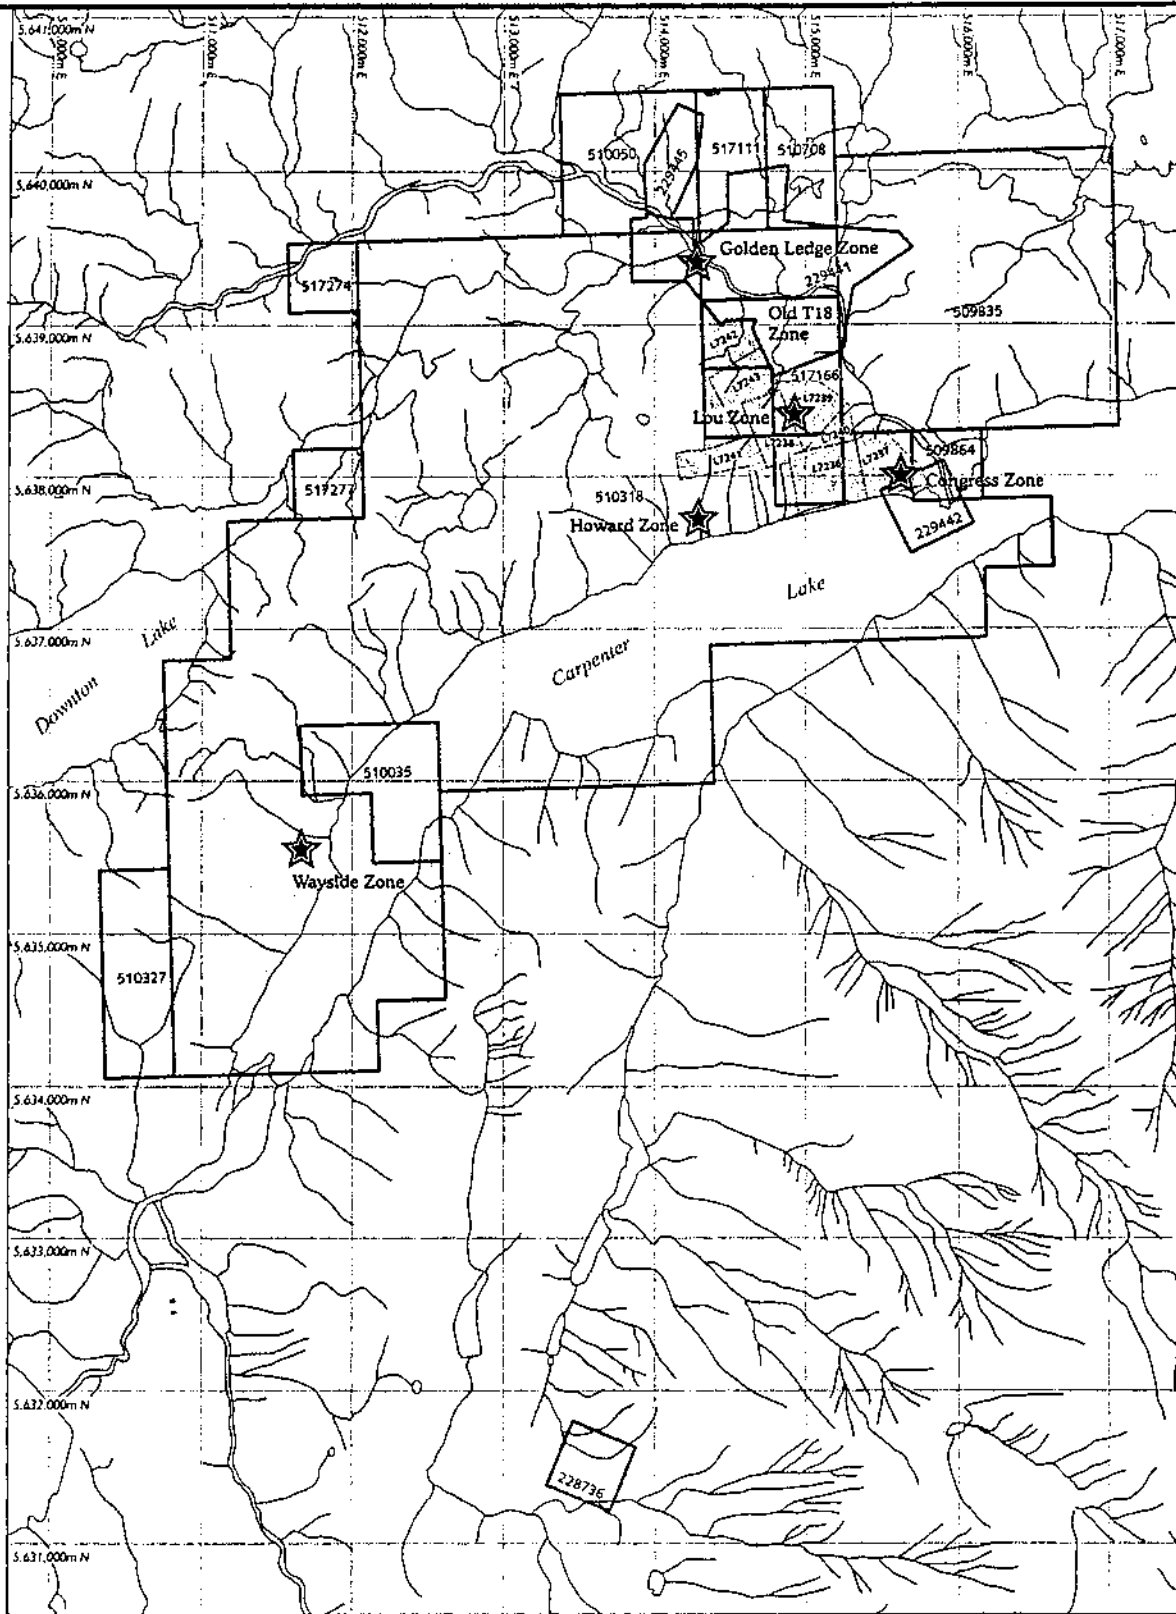

<b>Levon Resources Ltd.</b>			
<b>CONGRESS PROJECT</b>			
Lillooet M.D. British Columbia			
<b>Claim Location Map</b>			
Scale	1:50,000	UTM	NAD27 Zone 10
Date	April 2006	TRN	921.086.087.096.097
By	DSD/AGB	NTS	921/15
			<b>2</b>

### **3. Accessibility, Climate, Local Resources, Infrastructure and Physiography**

The property is easily accessible from Vancouver by all weather government maintained roads. Proceed north from Vancouver on paved Highway 99 through Squamish, Whistler and Pemberton 233 kilometres to Lillooet, then proceed west 96 kilometres on Highway 40 to the property (Fig. 1). Highway 40 is approximately 80% paved from Lillooet to the property and is maintained and ploughed year round, mainly for logging and tourist access. This route takes approximately 5.5 hours driving time. Alternatively in spring summer and fall, it is possible to drive to Pemberton on Highway 99 then northwest 20 kilometres to Pemberton Meadows and northeast 50 kilometres over the gravel Hurley River Forest Access Road to the property. This route takes approximately 4.5 hours driving time from Vancouver, but the road is not ploughed in the winter. All services necessary to operate a mine are available in Lillooet or Pemberton.

The property lies on the boundary between West Coast Marine and Interior climatic zones and is in the rain shadow created by the Coast Mountains. Precipitation is moderate, with generally warm, dry summers. Moderate to heavy snowfall occurs in winter months, with accumulations exceeding 2 metres on the property. Surface work is generally curtailed during winter months due to these conditions.

The town of Bralorne lies 16 kilometres southwest of the main showings on the property. This town was built to support historic mining operations and had a population of approximately 5,000 during historic operations. There are approximately 50 full time residents now and over 100 structurally sound houses in the town. The town of Goldbridge lies 5 kilometres southwest of the main showings on the property. Goldbridge has an area population of approximately 200. There are two motels, a restaurant, gas station, grocery store, and kindergarten to grade 7 school in Goldbridge. There are some trained miners living in the Bridge River Valley.

The towns of Bralorne and Goldbridge are connected to the B.C. electric power grid. The Lajoie Dam and power generation facility on Downtown Lake, operated by BC Hydro, are located approximately 4 kilometres west of the main showings on the property. A high tension power line follows Highway 40 across the property.

The property lies in mountainous terrain with deeply incised stream valleys and moderate to steep slopes. The property covers a plateau north of Carpenter Lake and a steep cliff and talus covered slope extending down to the lake edge. The Gun Creek canyon, 100 to 200 metres wide and 100 to 200 metres deep, crosses northwesterly across the northeastern quadrant of the property. Elevations range from 655 metres on Carpenter Lake in the south part of the property to 1,035 metres on the plateau in north central part of the property. Vegetation on the property consists of mature spruce, pine and interior fir. Approximately 60% of the property has been clear cut.

The local population is generally pro-mining and would like to see a mine developed for the benefits it would generate for the local communities.

Sufficient water for mining and milling purposes is available from Gun Creek in the eastern part of the property and a number of ponds and swamps on the plateau part of the property.

#### **4. History**

The Congress Zone was discovered in 1913 and has been explored and mined intermittently since then. Significant periods of activity occurred in 1933, when a 1,000 ton bulk sample was mined for metallurgical tests, and 1945 – 1950, when the vein was developed on 5 underground levels and some mineralized material stoped.

The Howard Zone was discovered in 1959 and explored by Bralorne-Pioneer Mines Ltd. who put in approximately half of the Lower Howard workings between 1960 and 1964. Levon Resources Ltd. carried out surface and underground drilling and drifting between 1976 and 1988 when the rest of the Lower Howard and the Upper Howard workings were excavated.

The Lou Zone was discovered by following up on soil geochemical anomalies and VLF-em geophysical anomalies in 1984. Extensive surface drilling was carried out from 1984 to 1988 and a 300 metre trackless decline was driven in the footwall of the zone in 1989.

Significant work was suspended until 2004 because of low gold prices. A mechanized trenching program on the northern extensions of the Lou and Congress zones was carried out in the fall of 2004. A diamond drill program was carried out on the Howard Zone in December 2004 and January 2005.

The 2004 surface exploration program consisted of approximately 120 metres of mechanized trenching in 6 trenches and 4 NQ diamond drill holes totaling 820.5 metres. The trenches were targeted at new mineral occurrences uncovered by logging activity in the central part of the property and on historic soil geochemical anomalies on strike with the projected northern extensions of the Lou and Congress zones. Drilling was targeted at better defining the Howard Zone north of the face of the Lower Howard drift.

Exploration in 2005 carried out by the company consisted of 2 pits, 27 trenches totaling approximately 300 metres, 6 NQ diamond drill holes totaling 1,060.68 metres and 102 MMI geochemical samples on seven lines.



## **5. Geological Setting**

The property covers Mississippian to Middle Jurassic rocks of the Bridge River Complex, mainly submarine basalt and andesite, with minor chert, argillite and mafic intrusives (Fig.3, Map 1). These rocks are cut by northwest trending regional scale structures, some with contained Tertiary feldspar porphyry dacite dykes, sub-parallel to the Ferguson and Cadwallader Structures, which bound the historic Bralorne/Pioneer mines. The structures on the property are roughly the same distance from the Upper Cretaceous-Tertiary granite Bendor Intrusions as the Bralorne/Pioneer mines. The Bendor Intrusions are the same age as the mineralization in the Bralorne/Pioneer mines and are a postulated source for the gold mineralization at these mines and on the Congress Property.

## **6. Deposit Types**


The deposits on the company's property are members of a well recognized group of deposits referred to as mesothermal, orogenic or greenstone hosted quartz-carbonate gold vein deposits. These deposits include the Mother Lode and Grass Valley districts in California and most of the greenstone hosted gold deposits in the Canadian Shield, including the Timmins-Val d'Or, Red Lake and Hemlo camps. These deposits are quartz-carbonate veins in moderately to steeply dipping brittle-ductile shear zones and, locally, in shallow dipping extensional fractures.

## **7. Mineralization**

Mineralization in the Howard Zones consists of quartz-carbonate veins or stringer zones one to 1.5 metres wide, with altered, mineralized selvages (pyrite, siderite) up to 10 metres total width hosted in basalt and gabbro. The zones strike north to a few degrees west of north and dip steeply to the west. The Howard Zones contain the largest and highest grade resource on the property, with over 100,000 ounces of gold contained in all resource categories totaling more than 300,000 tonnes greater than 20 grams per tonne gold. These resources are refractory and would require oxidation of sulphides to recover the gold.

Mineralized areas in the Lou Zone are stockwork quartz carbonate stringers and silicified zones on the flank of a feldspar porphyry dyke hosted in mafic volcanics. The zone strikes north and dips steeply west. The better mineralized zones are 1.5 to 4.0 metres wide and grade 5 to 11 grams gold/tonne and contain abundant stibnite. The Lou Zone has been oxidized for 2 to 5 metres below surface near the decline portal where an open pit resource has been outlined.

The better mineralized areas in the Congress Zone, including the 2004 trenches, are massive stibnite veins, 1.25 to 1.5 metres wide, grading 6 to 8 grams gold per tonne hosted in argillite, chert and very sheared mafic volcanic rocks and again, striking north and dipping steeply west.

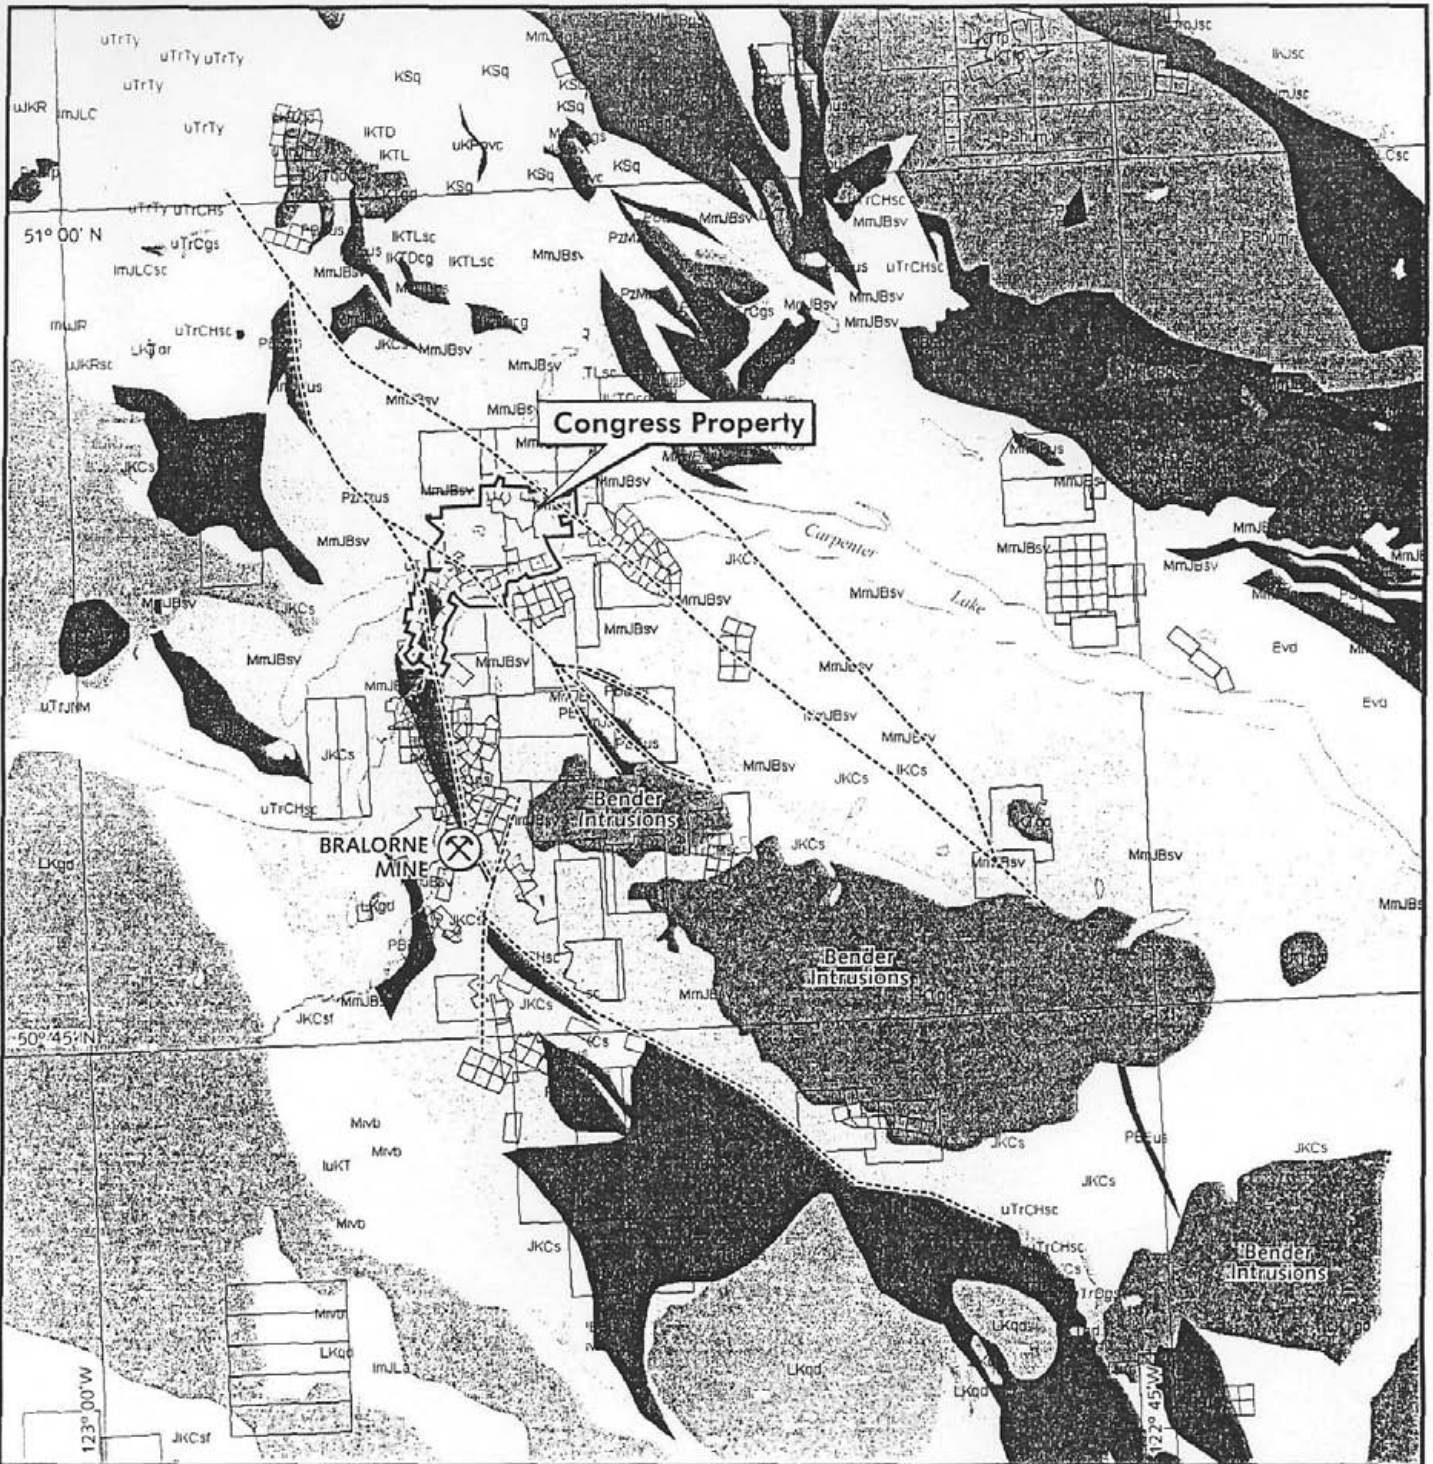

**Congress Property**

**BRALORNE MINE**

**Bender Intrusions**

**Bender Intrusions**

**Bender Intrusions**

**Lithological Legend**

- Mivb Miocene unnamed: basaltic volcanic rocks
- Efd Eocene: unnamed feldspar porphyritic intrusive rocks
- Egd Eocene: unnamed granodioritic intrusive rocks
- Evd Eocene: unnamed dacitic volcanic rocks
- LKTgd Late Cretaceous to Paleogene: unnamed granodioritic intrusive rocks
- LKgd Late Cretaceous: unnamed granodioritic intrusive rocks
- LKqd Late Cretaceous: unnamed quartz granodioritic intrusive rocks
- uKPo Upper Cretaceous: Powell Creek Formation - undivided volcanic rocks
- IKTs Lower Cretaceous: Taylor Creek Group - undivided sedimentary rocks
- luKT Lower Cretaceous to Upper Cretaceous: unnamed volcanoclastic rocks
- uJKRsc Upper Jurassic to Lower Cretaceous: Relay Mountain Group - undivided sedimentary rocks
- JKCsf Jurassic to Cretaceous: Cayoosh Assemblage - undivided sedimentary rocks
- uTrTy Upper Triassic: Tyaughton Group - conglomerate, coarse clastic sedimentary rocks
- uTrCHsc Upper Triassic: Cadwallader Group, Hurley Formation - undivided sedimentary rocks
- MmJBsv Mississippian to Middle Jurassic Bridge River Complex: marine sedimentary and volcanic rocks
- MmJBgs Mississippian to Middle Jurassic Bridge River Complex: greenstone, greenschist metamorphic rocks
- MmJBbs Mississippian to Middle Jurassic Bridge River Complex: blueschist metamorphic rocks
- PBEus Permian: Bralorne East Liza Complex: serpentinite ultramafic rocks
- PShum Permian: Shulaps Ultramafic Complex - Hartzburgite Unit: ultramafic rocks
- PShus Permian: Shulaps Ultramafic Complex - Serpentine Melange Unit: serpentinite ultramafic rocks
- PzMzus Paleozoic to Mesozoic unnamed serpentinite ultramafic rocks
- ?gb Age Unknown: gabbroic to dioritic intrusive rock

**Symbol Legend**

--- geological fault



(source: <http://webmap.em.gov.bc.ca/mapplace/minpot/bcgs.cfm>)

**Levon Resources Ltd.**

**CONGRESS PROJECT**

Lillooet M.D. British Columbia

**Regional Geology Map**

Scale	as shown	UTM	NAD83 Zone 10	fig <b>3</b>
Date	April 2006	TRIM	92J.086.087.096.097	
By	DSD/AGB	NIS	92J/15	

## **8. Other District Properties**

The most important adjacent properties are the northwest trending low sulphidation, mesothermal quartz veins, variably mineralized with auriferous pyrite, arsenopyrite, galena, sphalerite, chalcopyrite and free gold of the Bralorne and Pioneer Mines, located 11 kilometres south of the property. These mines have the largest reported gold production in the Canadian Cordillera with 129.24 tonnes of 4,155,627 ounces of gold recovered from 7.2 million tonnes averaging 17.95 grams gold per tonne. Productive veins were typically 1.3 metres to 2.5 metres in width, with ore shoots locally up to 6.0 metres in width. The best ore shoot in the Pioneer Mine was mined over 800 metres vertically and 400 metres horizontally. These are "true fissure veins", following regional scale structures and exhibiting good vertical and horizontal continuity. The best ore shoots occur in the northwest trending ribbon veins where there is a flexure in the vein or where the veins are in contact with or cutting serpentinite.

This is the type of mineralization sought on the company's property.

## **9. 2006 Diamond Drilling**

A program of 16 NQ diamond drill holes totaling 2,418.8 metres was carried out on the property from October 4<sup>th</sup> to December 3<sup>rd</sup>, 2006.

Five holes GI-06-01 to GI-06-05 were drilled to explore the Golden Ledge Zone in the north part of the property.

Nine holes LZ-06-01 to LZ-06-09 explored the Lou Zone.

Two holes C-06-01 and C-06-02 were drilled on the Howard Zone.

Principal intersections on the vein structures are shown in the following table. The drill logs are attached in Appendix B. Assay results are in Appendix C.

Core is stored on racks at the Bralorne Pioneer Property.

## LEVON CONGRESS 2006 DRILL RESULTS

Hole	Location UTM		Bearing	Dip	Length Metres	Intersection Metres	Gold gm/tonne	Arsenic ppm
	Northings	Eastings						
<b>Golden Ledge Zone</b>								
GL-06-01	5639328	514291 E	350	45	166.37	68.0 - 69.0 (1) 72.0 - 75.0 (3) 91.0 - 92.0 (2) 122.0 - 124.0 (2)	3.08 6.41 4.17 4.71	>10,000 >10,000 >10,000 >10,000
GL-06-02A GL-06-02B					41.76 17.37	(Drill Problems - Abandoned)		
GL-06-02	5639411	514285	190	50	81.40	51.0 - 53.0 (2)	5.66	>10,000
GL-06-03	5639411	514285	190	60	72.24	45.0 - 46.0 (1)	5.48	>10,000
GL-06-04	5639338	514267	010	45	102.72	88.0 - 89.0 (1)	3.38	4,490
GL-06-05	5639338	514267	010	60	121.01	66.44 - 67.50 (1.06) 71.0 - 71.75 (0.75)	3.80 2.38	8,795 >10,000
<b>Vanadium Zone</b>								
LZ-06-01	5638871	514799	88	50	99.67	52.50 - 53.0 (0.5)	4.21	2,258
LZ-06-02	5639045	514861	90	45	117.96	<b>NO SIGNIFICANT VALUES (NSV)</b>		
LZ-06-03	5638291	514764	90	45	203.30	150.0 - 152.50 (2.0) 178.0 - 180.0 (2.0)	4.40 1.71	3,587 3,326
LZ-06-04	5638227	514760	90	45	157.02	<b>(NSV)</b>		
LZ-06-05	5638124	514759	90	55	185.01	132.0 - 134.0 (2.0) 139.86 - 142.0 (2.14)	2.55 1.03	1,852 1,588
LZ-06-06	5638076	514753	96	45	194.16	151.5 - 153.5 (2.0)	2.94	3,398
LZ-06-07	5638076	514753	106	45	178.92	155.0 - 158.0 (3.0)	7.28	3,983
LZ-06-08	5638076	514750	106	60	203.30	162.0 - 163.0 (1.0)	1.59	672
LZ-06-09	5637426	514671	060	45	163.68	<b>(NSV)</b>		
C-06-01	5637430	514321	100	45	151.51	<b>(NSV)</b>		
C-06-02	5637433	514321	90	55	159.39	115.0 - 116.0 (1.0) 153.0 - 154.0 (1.0)	0.67 10.70	3,313 >10,000

## 10. Sample Preparation, Analysis and Security

Mineralized sections of drill core were sampled, generally to lithological or alteration boundaries. Two metres or less of core was split on site with a manual Longyear core splitter and half core splits placed in 6 mil plastic bags with a unique sample tag. The tag number was then written twice on the outside of the bag and the bags sealed with winter grade flagging. Core recovery was greater than 95% for all holes. The remaining core was stored in a secure core storage facility at the Bralorne Mines Ltd. office and mill site.

1. The drill programme ran October and November 2006 under supervision by Chris J. Sampson, P.Eng., Qualified Person for NI 43 101 using the standard practices required.
2. Samples from holes GL-06-01, 02, 03, 04, 05 and hole LZ-06-01 were assayed at EcoTech Labs – Kamloops, British Columbia, Canada. Remaining holes LZ-06-02 through LZ-06-09 and C-06-01 and 02 were assayed at Assayers Canada Limited, Vancouver, British Columbia, Canada.

In both cases the labs used Standard Fire Assay with I.C.P. Aqua Regia Leach Finish.

## 11. Conclusions and Recommendations

The 2006 drilling programme extended both the Golden Ledge (to the west) and Lou Zones (to the north).

A programme of trenching and drilling is recommended for 2007 to further explore the Golden Ledge, Lou and other zones (Howard, Paul, Ozone etc.)

Estimated costs would be as follows:

10 trenches (25 m length) (including supervision assays etc.)	\$40,000
12 diamond drill holes (NQ, average 150 m length) plus supervision assays reclamation	<u>\$360,000</u>
<b>Total</b>	<b>\$400,000</b>

## 12. References

- Ash, C. 2001: *Ophiolite Related Gold Quartz Veins in the North American Cordillera*, British Columbia Geological Survey Branch, Bulletin 108.
- Ash, C. and Alldrick, D., 1996: Au-Quartz Veins; in Selected British Columbia Mineral Deposit Profiles, Volume 2, D.V. Lefebure and T. Hoy, Editors, *British Columbia Ministry of Energy, Mines and Petroleum Resources*, pages 53-56.
- Chapman, Wood and Griswold Ltd., 1965: *Memorandum Reports Nos. 1, 2, and 3 Ace Mining Co. Ltd.*
- Church, B.N., 1996: *Bridge River mining camp, geology and mineral deposits*; British Columbia Geological Survey Branch, Paper 1995-3, 159 p.
- CIM, 1976: Special Volume 15; *Porphyry Deposits of the Canadian Cordillera*, A. Sutherland Brown, Editor.
- Christofferson, J.E., 1987: *Status Report on the Congress Property*.
- Christofferson, J.E., 1988: *Report on Gold Ore Reserves, Congress Property*.
- CIM, 1995: Special Volume 46; *Porphyry Deposits of the Northwestern cordillera of North America*, T.G. Schroeter, Editor.
- Dolmage, Mason and Stewart Ltd., 1964: *Report on Examination of the Ace Mining Property*.
- Dolmage, Mason and Stewart Ltd., 1965: *Ace Mining Company Limited N.P.L., Final Report*.
- Emmons, W.E., 1937: *Gold Deposits of the World*, pages 99 – 100.
- Geological Survey of Canada, 1995: *Geology of Canada*, no. 8: Geology of Canadian Mineral Deposit Types, pages 324, 328, 351 – 357, 360, 363. O.R. Eckstrand, W.D. Sinclair, and R.I. Thorpe, Editors.
- Martin, W., 1961: *Ore Potentialities Bralorne Pioneer Mines Limited*, Unpublished Report.
- Miller-Tait, J., and Sampson, C., 1995: *Exploration and Development Programmes, October 1993 – July 1995, Bralorne-Pioneer Property, Bralorne, British Columbia, Lillooet Mining Division, Bridge River Area, NTS 92-j/15, Latitude 50° 46' N, Longitude 122° 48' W*.
- Miller-Tait, J., Morris, A., and Hawthorn, G., 1996: *Bralorne Pioneer Gold Mines Ltd., Plan and Production Schedule for: 150 Ton per Day Mining Operations, Bralorne Gold Mine, Bralorne, B.C.* Unpublished Corporate Report.
- Mindat Consultants, 1984; *Progress Report on the Congress Property*.
- Process Research Associates Ltd., 2003. *Project 0304003, 0304006, 0403504*. Unpublished company reports.
- Sawyer Consultants Inc., 1979; *Report on the Howard Property*.
- Seraphim, R.H., 1981; *Progress Report Bridge River Claims of New Congress Resources Ltd.*
- Schiarrizza, P., Gaba, R.G., Glover, J.K., Garver, J.I., and Umhoefer, P.J., 1996: *Geology and Mineral occurrences of the Taseko-Bridge River Area; Geological Survey of British Columbia, Bulletin 100*.

## Appendix A

### Statement of Costs

#### Diamond Drill Invoiced Costs:

<b>October 16, 2006, ABC Drilling Invoice</b>	<b>121,895.60</b>
<b>October 20, 2006, ABC Drilling Invoice</b>	<b>40,383.29</b>
<b>November 16, 2006, ABC Drilling Invoice</b>	<b>70,458.18</b>
<b>November 30, 2006, ABC Drilling Invoice</b>	<b>136,205.87</b>
	<b>368,942.94</b>

## Appendix B

### Diamond Drill Logs

HOLE	LOCATION UTM		DEPTH	DIP
	NORTHINGS	EASTINGS		
GOLDEN LEDGE ZONE				
GL-06-01	5639328	514291 E	350	45
GL-06-02A GL-06-02B	Abandoned			
GL-06-02	5639411	514285	190	50
GL-06-03	5639411	514285	190	60
GL-06-04	5639338	514267	010	45
GL-06-05	5639338	514267	010	60
LOU ZONE				
LZ-06-01	5638871	514799	88	50
LZ-06-02	5639045	514861	90	45
LZ-06-03	5638291	514764	90	45
LZ-06-04	5638227	514760	90	45
LZ-06-05	5638124	514759	90	55
LZ-06-06	5638076	514753	96	45
LZ-06-07	5638076	514753	106	45
LZ-06-08	5638076	514750	106	60
LZ-06-09	5637426	514671	060	45
HOWARD ZONE				
C-06-01	5637430	514321	100	45
C-06-02	5637433	514321	90	55



DRILL HOLE RECORD		CLAIM	BEARING	DIP	SURVEY TYPE	CORE SIZE: NO	HOLE # GL-06-01
COMPANY: LEVON RESOURCES LTD.		LOCATION	350°	45°	stn	STARTED: OCT 4 / 06	SHEET: 1 of 6
PROJECT: Congress-Golden Ledge		ELEVATION				COMPLETED: OCT 7 / 06	FINAL DEPTH: 166.37
UNITS metric	LATITUDE 5639328 N	DEPARTURE 514291 E				LOGGED BY: CK	

DEPTH		LOG	DESCRIPTION	Sample No.	FROM	TO	CORE INT.	SAMP INT.	Au/g	Au/oz ft	AS ppm
FROM	TO										
0	16.83		CASING	143501	57.39	58	2.61	0.61	2.03		25
					58	59	1.0	1.0	<.03		5
16.83	33.64		VOLCANIC (basalt) light green to green 21.05-21.38 banded & lapilli size frags qtz/carb veining (2.5mm)	143505	59	60	1.0	1.0	<.03		5
			22.51-22.71 flow banding		60	61	1.0	1.0	<.03		
			26.41-28.19 poor recovery FAULT		61	62	1.0	1.0	<.03		<5
			29.11-31.97 transition to alteration zone bleached, milky qtz random orient.		62	63	1.0	1.0	<.03		<5
			31.97-33.07 fragmented qtz/carb veining	143510	63	64	1.0	1.0	<.03		5
			33.07-35.41 30% 7 10cm TRANSITION TO ALTERATION ZONE VOLCANICS chloritic alt. fragmented, large 5cm narrow frags, light/pale green matrix. flow banded, hematite qtz/carb veining various orient, tr py		64	65	1.0	1.0	<.03		10
					65	66	1.0	1.0	<.03		15
					66	67	1.0	1.0	<.03		25
					67	68	1.0	1.0	<.03		430
					68	69	1.0	1.0	3.68	0.107	>10000
33.64	35.41				69	70	1.0	1.0	<.03		17
					70	71	1.0	1.0	<.03		60
					71	72	1.0	1.0	<.03		125
					72	73	1.0	1.0	3.30	0.09	90
					73	74	1.0	1.0	8.45	0.246	71000
					74	75	1.0	1.0	7.49	0.218	71000
35.41	61.76	88	VOLCANICS - chloritic / fragmented light to dk grn, waxy qtz/carb veining tr py	143520	75	76	1.0	1.0	<.03		9070
					76	77	1.0	1.0	<.03		55
					77	78	1.0	1.0	<.03		100
					78	79	1.0	1.0	<.03		25
					79	80	1.0	1.0	<.03		25
					80	81	1.0	1.0	<.03		25

g/t

DEPTH		LOG	DESCRIPTION	Sample No.	FROM	TO	CORE INT.	SAMP INT.	Au	Au	Hole#GL-08-01	
FROM	TO								ppm	oz/t	Sheet	AS
61.76	78.40		TRANSITION TO ALTERATION ZONE	143525	81	82	1.0	1.0	<0.03			<5
			light tan colored volcanics, siliceous fractured, some flow banding		82	83	1.0	1.0	<0.03			<5
			15% qtz/carb veinlets, ankentic alter.		83	84	1.0	1.0	<0.03			5
			84	85	1.0	1.0	<0.03					25
		A7	62.33-62.5 flow banding w/tr-1% diss. py		85	86	1.0	1.0	<0.03			1295
			63.33-68.68 lapilli sized frags dk green matrix, 15-20% milky qtz veining, various orientations tr py	143526	86	87	1.0	1.0	<0.03			20
			87	88	1.0	1.0	<0.03					<5
			88	89	1.0	1.0	0.05					1045
			89	90	1.0	1.0	1.13	0.033				3090
			90	91	1.0	1.0	4.57	0.133				>10000
			65.79-68.70 3-5% fine grained py as fracture fills, tr arsp, tr blebby py	143525	91	92	1.0	1.0	3.76	0.110		>10000
			92	93	1.0	1.0	0.14	0.04				1235
			93	94	1.0	1.0	0.39	0.011				3870
			72.0-75.29 2-3% py as fracture fills & veinlets		94	95	1.0	1.0	0.04	0.016		265
			95	96	1.0	1.0	<0.03					2895
			73.29-74.15 FAULT - Poor Recovery	143520	96	97	1.0	1.0	<0.03			20
		RQ	30% >10cm		97	98	1.0	1.0	<0.03			10
			98	99	1.0	1.0	<0.03					5
78.40	79.14		MEDIUM GREEN VOLCANICS - fine grained chloritic, 10% random qtz veins tr diss py	143528	99	100	1.0	1.0	<0.03			5
			100	101	0.5	0.5	<0.03					5
			101	102	1.0	1.0	<0.03					5
			TAN		106	107	1.0	1.0	<0.03			<5
79.14	81.39		ALTERED VOLCANICS - sm. frags, minor flows, 1% diss py		107	108	1.0	1.0	<0.03			90
			108	109	1.0	1.0	<0.03					115
			109	110	1.0	1.0	<0.03					105
81.39	82.79		TRANSITION TO MED GREEN VOLCANICS fine grained, 5% irregular qtz veins	143520	110	111	1.0	1.0	0.41			2945
			111	112	1.0	1.0	0.31					2525
			112	113	1.0	1.0	<0.03					5
82.79	83.46		ALTERED TAN VOLCANICS, fine grained fractured, sm. flows, tr py ankentic alter'n		113	114	1.0	1.0	<0.03			5
			114	115	1.0	1.0	<0.03					5
			115	116	1.0	1.0	<0.03					5









DEPTH			LOG	DESCRIPTION	Sample No.	FROM	TO	CORE INT.	SAMP INT.	Au <del>oz/l</del>	Au oz/l	As ppm
FROM	TO											
0.0	3.95			CASING						916		
3.95	13.38			LIGHT TO MED GREEN VOLCANICS W/ MAROON VOLCANICS - FINE GRAINED FRACTURED QTZ/CARB VEINING (5%) RANDOM ORIENTATIONS 9.50-11.00 LG MAROON LAPILLI SIZE FRAGS								
				RQ 65% ≥ 10 CM - POOR RECOVERY ARGILL 9.3-9.8								
13.38	13.82			TAN ALTERED VOLCANICS - BRECCIATED W/ ARGILLITIC MATRIX / ANKERITIC ALT'N	14364	13.30	14.00	0.7				
				5% QTZ/CARB PERVASIVE	14357	14.50	15.50	1.0		1.08		7110
				13.51 - 13.70 - 2-3% PY AS FRACTURE FILLS	14345	15.90	16.80	0.9				
					14346	19.0	20.0	1.0				
13.82	16.44			LIGHT TAN ALTERED VOLCANICS - FINE GR FRACTURED W SM. FLOWS								
				5% QTZ/CARB VEINING								
				65° 14.75-14.92 SM. DYKE ALT. VOLC IN ARGILLITIC MATRIX								
				16.00-16.44 5% PY AS SM. (≥ 3MM)								
				FRACTURE FILLS & FINE GR. DISSEMINATIONS								
				TR ARSP								
16.44	29.40			LIGHT TO DK GREEN VOLC. W/ SMALL TAN ALTERED VOLC APHANITIC - FRACTURED / AMYG. FLOWS								
				5% QTZ/CARB VEINING - RANDOM								
				18.68-18.75 GOUGE								

DRILL HOLE RECORD

COMPANY: LEVON RESOURCES LTD	CLAIM LOCATION	COLLAR	BEARING	DIP	SURVEY TYPE	CORE SIZE: NO	HOLE # GL-06-02
PROJECT: CONGRESS - GOLDEN LEDGE	ELEVATION 744M		190°	-50°	str	STARTED: OCT 9/06	SHEET: 1 of 3
UNITS Metric	LATITUDE 563941 N					COMPLETED: OCT 10/06	FINAL DEPTH: 21.40
	DEPARTURE 514285 E					LOGGED BY: CK	

915 GL

DEPTH		LOG	DESCRIPTION	Sample No.	FROM	TO	CORE INT.	SAMP INT.	Au	Au	06-02
FROM	TO								ppm	oz./t	Sheet
			18.78-20.00 ALTERED TAN VOLCANICS	143581	28.50	29.31	0.81	0.81	20.07		15
			FRACTURED 2-3% DISS PY	143582	34.30	35.0	0.7	0.7	20.03		10
		65°	CONTACT W/ GREEN VOLCANICS 18.78	143583	35.00	36.00	1.0	1.0	<0.03		<5
			24.13-24.30 SM ALTERED VOLCANIC	143584	36.00	37.00	1.0	1.0	<0.03		20
			FLOW SM ≥ 3MM FRAGS IN ARG. MATRIX	143585	37.00	37.70	0.7	0.7	0.07		705
			28.52-29.31 - TAN ALTERED VOLCANICS								
			W/ SOME MAROON LAPILLI SIZE FRAGS								
			2-3% PY AS FRACTURE FILLS								
		67°	29.31-29.40 TRANSITION TO UNALTERED VOLC.								
29.40	38.72		DK GREEN/MAROON VOLCANICS								
			FINE GRAINED, BRACIATED SM FLOWS								
			(FRAGS ≥ 3MM), SERP.(TALC) ALT'N								
			QTZ/CARB VEINING (5-7%)								
			34.80-35.40 MAROON LAPILLI SIZE								
			FRAGS IN DK MATRIX, 3-5% PY PERVASIVE								
38.72	43.56		DARK GREEN VOLCANICS - FINE GRAINED,								
			CHLORITIC, FRACTURED								
			10% QTZ CARB FLOODING - RANDOM								
			ORIENTATIONS								
43.56	53.17		TAN ALTERED VOLCANICS (ANKERITIC	143586	43.80	45.00	1.20	1.20	<0.03		20
			ALT'N) FINE GRAINED, FRACTURED/	143587	45.00	46.00	1.0	1.0	20.03		10
			FLOWS - DK (ARGILLITIC MATRIX)	143588	46.00	47.00	1.0	1.0	20.03		10
			5% QTZ/CARB STRINGERS	143589	47.00	48.00	1.0	1.0	20.03		<5
			48.40-48.72 - 3-5% PY AS FRACTURE	143590	48.00	49.00	1.0	1.0	20.03		40
			FILLS & DISSEM., TR ARSPY, SB								

15 ppm



9/5 GL

DEPTH		LOG	DESCRIPTION	Sample No.	FROM	TO	CORE INT.	SAMP INT.	Au	Au	96-02	
FROM	TO								ppm	oz./t	Sheet	3 A5
		72°	51.35-52.86 - SM DYKE, SM. FRAGS (≥3MM)	143591	49.00	50.00	1.0		<0.03			35
			IN ARGILLITIC MATRIX 3-5% PY AS LG	143592	50.00	51.00	1.0		<0.03			285
			(≥5MM) FRACTURE FILLS, 1% DISS ARSPY	143593	51.00	52.00	1.0		4.5			>10000
			51.74 - 51.77 - SB VEIN	143594	52.00	53.00	1.0		6.75			>10000
53.77	79.89		DK GREEN / MAROON VOLCANICS, SOME ALT VOLC	143595	53.00	54.00	1.0		<0.03			30
			APHANITIC, FRACTURED / FLOWS									
			53.70-65.70 10-15% QTZ/CARB.									
			VEINING / STRINGERS									
			65.80-73.50 MIXED DK GREEN (CHLORITIC)									
			VOLCANICS + MAROON VOLCANICS, LAPILLI	143596	68.01	68.51	0.50	0.50	20.03			20
			SIZE FRAGMENTS IN ARG MATRIX 2-3% PY	143597	72.00	72.50	0.50	0.50	<0.03			10
		67°	74.00-74.30 ARGILLITE CONTACT	143598	74.00	75.00	1.00	1.00	0.03			100
			CALCAREOUS, BROKEN, SHATTERED	143599	77.50	78.40	0.90	0.90	<0.03			35
			2-3% PY AS SM. (≥2MM) VEINLETS	143600	80.0	80.5	0.5	0.5	0.20			1165
			77.75-78.40 ARGILLITE W/ TAN ALTERED									
			VOLCANICS SM VOLC FRAGS (≥2MM)									
			1-3% PY									
79.81	81.40		ARGILLITE - GRAPHITIC / CALCAREOUS									
			5% QTZ / CARB - VARIOUS ORIENTATIONS									
81.40			E.O.H									

ppm





910

DEPTH		LOG	DESCRIPTION	Sample No.	FROM	TO	CORE INT.	SAMP INT.	Au <del>oz.</del>	Au oz./ft	GLO6-Sheet:	03 3
FROM	TO											
			30.80-31.39 TAN ALTERED VOLCANIC FINE GRAINED, MICRO-FRACTURED								As ppm	
			31.24 LG 1/3 CM QTZ VEIN 70° TO CA TR PY									
31.39	32.96		DK GREEN VOLCANICS FRACTURED / FLOWS FINE GRAINED 5-10% QTZ CARB. VARIOUS ORIENTATIONS 31.32-31.97 FLOW, SM → ZMM FRACS, BLK GRAVIMASS TR-1% FINE DISS. PY									
			55° 32.96 CONTACT W/ TAN ALTERED VOLCANICS									
32.96	48.44		TAN/GRAY ALTERED VOLCANICS APHANITIC, FRACTURED / FLOWS 5-10% QTZ CARB VEINING, ANKERITIC ALT'N LG → 10MM LAMELLI SIZE FRACS PERMISSIVE	143607	33.95	35.00	1.05	1.05	20.03		175	
			33.00-31.96 5-10% AS VEINS, FRACTURE FILLS, 1-2% ARSPY AS FINE DISSEM.	143608	35.0	36.0	1.0	1.0	0.87		9425	
			38.52-38.71 LIGHT GRAY/TAN ALTERED VOLC. MICRO-FRACTURED 2% DISS PY, 1% ARSPY	143609	36.0	37.0	1.0	1.0	20.03		45	
			40.90-41.98 QTZ VEIN 80° TO CA, 1% DISS PY	143610	37.0	38.0	1.0	1.0	20.03		145	
			41.00-42.98 MICRO FRACTURED/FLOWS 2-5% DISS PY, TR ARSPY	143611	38.0	39.0	1.0	1.0	20.03		20	
			46.49 47.09 - 5-10% PY, 1-2% ARSP, 47.10-47.09-47.18 SB VEIN	143612	39.0	40.0	1.0	1.0	20.03		15	
			RQ 75% → 10 CM	143613	40.0	41.0	1.0	1.0	0.11		1625	
48.44	72.24		DK GREEN/MAROON VOLCANICS BRECCIATED / FLOWS 5-7% QTZ/CARB VEINING / FINE GRAINED / SERP/TALC ALT'N	143614	41.0	42.0	1.0	1.0	20.03		45	
			49.80-49.86 SM. ALTERED VOLCANIC	143615	42.0	43.0	1.0	1.0	20.03		50	
				143616	43.0	44.0	1.0	1.0	20.03		110	
				143617	44.0	45.0	1.0	1.0	0.04		215	
				143618	45.0	46.0	1.0	1.0	5.48		<10000	
				143619	46.0	47.0	1.0	1.0	0.20		3305	
				143620	47.0	48.0	1.0	1.0	20.03		25	

ETNA



DRILL HOLE RECORD		CLAM		BEARING	DIP	SURVEY TYPE	CORE SIZE: NO	HOLE: GL0604
LEVOY RESOURCES		LOCATION	COLLAR	10°	45°	str	STARTED: 12/10/06	SHEET: 1 of 3
COMPANY: BRALORNE GOLD MINES	ELEVATION 770M		COMPLETED: 13/10/06				FINAL DEPTH: 122.72	
PROJECT: 2889 SCHNEE GOLDMINE	LATITUDE 5639338 N		LOGGED BY: CLK					
UNITS Imperial	METRIC	DEPARTURE 514267 E						g/t

DEPTH		LOG	DESCRIPTION	Sample No.	FROM	TO	CORE INT.	SAMP INT.	Au	Au	AS
FROM	TO										
0.0	21.34		CASING								
21.34	76.90		LIGHT TO DK GN VOLCANICS - FINE GRAINED, 5-7% QTZ/CARB. VEINING PERSASIVE - FRACTURED/FLOWS								
		RQ	21.34-27.50 Poor RECOVERY (25% @ 10CM)								
			33.20-33.32 QTZ/CARB FLOODING								
			34.64-35.61 LAPILLI SIZE FRAGS (MED. GREEN) IN DK GREEN SM. (> 2MM) FRAG. MATRIX TR DISS PY								
		50°	35.58 CONTACT W/ DK GREEN VOLCANICS								
			41.38-42.44 QTZ/CARB VEIN IN MED GREEN VOLCANICS 45% to CA								
			44.02-47.58 VOLCANIC FLOWS LAPILLI SIZE FRAGS W/ SM BLACK (ARGILLITIC) INCLUSIONS 2-3% QTZ CARB.								
			49.61-49.70 ANKERITIC ALT'N, QTZ CARB								
			53.42-53.53 GN VOLCANICS FINE GRAINED, QTZ/CARB, TR PY, HEMATITE								
			55.90-56.00 TAN VOLCANIC (ANKERITIC) ALT'N/ W/ QTZ-CARB VEIN (3 CM)	43622	56.16	57.16	0.86	0.86	<0.03	5	5
			45° to CA	143623	64.20	64.70	0.6	0.6	<0.03	<5	<5

DEPTH		LOG	DESCRIPTION	Sample No.	FROM	TO	CORE INT.	SAMP INT.	Au	Au	GL06- Sheet	04 2
FROM	TO								ppm	oz./t		
			58.32 - 66.14 LIGHT GN VOLCANICS MIXED W/ DK GREEN VOLCANICS, FRACTURED FLOWS 5% QTZ/CARB						915		As	
			61.0 - 61.08 QTZ CARB VEIN 65° TO CA 62.78 - 62.25 AMYGDALAR, QTZ/CARB VEINING TR PY								ppm	
			69.10 - 72.24 DK GREEN VOLCANICS W/ HEMATITE STAINING, FINE GRAINED, LAPILLI SIZE FRAGS, TR PY CHLORITIC 73.52-76.90 TRANSITION TO LIGHT GN VOLCANICS 80% > 10CM									
76.90	81.69		TAN ALTERED VOLCANICS (ANKERITIC ALT'N) FRACTURED/FLOWS, FINE GRAINED, CONTACT	143624	76.90	78.00	1.1	1.1	6.03		<5	
		85°	76.90 - 77.46 - LG (250 MM) LAPILLI SIZE FRAGS W/ (SM. > 5MM) FLOWS	143625	78.0	79.0	1.0	1.0	6.03		<5	
			79.40 - 79.45 QTZ/CARB VEIN 80° TO CA	143626	79.0	80.0	1.0	1.0	<0.03		<5	
			80.75 - 81.28 - CHLORITIC ALT'N, TR PY	143627	80.0	81.0	1.0	1.0	<0.03		<5	
			81.68 CONTACT W/ DK GN VOLCANICS	143628	81.0	81.70	0.7	0.7	<0.03		<5	
			83.32 CONTACT W/ ALTERED TAN VOLCANICS BRICKEN/FRACTURED 10% QTZ CARB., TR FINELY DISS. 12%	143629	83.33	84.0	0.67	0.67	<0.03		<5	
				143630	84.0	85.0	1.0	1.0	<0.03		<5	
				143631	85.0	86.0	1.0	1.0	<0.03		<5	
		60°		143632	86.0	87.0	1.0	1.0	<0.03		<5	
				143633	87.0	88.0	1.0	1.0	<0.03		10	
				143634	88.0	89.0	1.0	1.0	3.35		4490	
81.68	83.32		DK GREEN VOLCANICS - FINE GRAINED 5% QTZ VEINING PERIPHERAL - RANDOM ORIENTATIONS	143635	89.0	90	1.0	1.0	0.04		385	





DRILL HOLE RECORD		CLAM		BEARING	DIP	SURVEY TYPE	CORE SIZE: NO	HOLE # GL-06-5
COMPANY: LEVON RESOURCES LTD	LOCATION		COLLAR	10°	60°	str	STARTED: 12/10/06	SHEET: 1 of 3
PROJECT: CONGRESS - GOLDEN LEDGE	ELEVATION 770M						COMPLETED: 13/10/06	FINAL DEPTH: 121.01
UNITS Metric	LATITUDE 5639238 N						LOGGED BY: CK	
	DEPARTURE 514267 E							

DEPTH		LOG	DESCRIPTION	Sample No.	FROM	TO	CORE INT.	SAMP INT.	Au oz./t	Au oz./t
FROM	TO									
0.0	12.19		CASING							
12.19	41.76		LIGHT TO DK GREEN VOLCANICS - FINE GRAINED W/ ARGILLITIC INCLUSIONS 3-5% QTZ - CARB VEINLETS / BRECCIATED / FLAKES RQ SOFT, POOR RECOVERY 18.0-20.42 (90% > 10cm) RQ 24.35-36.40 (15% > 10cm) 37.43-37.85 - QTZ / CARB FLOODING 2cm QTZ CARB VEIN 75° to CA 38.90-41.52 DK GN VOLCANICS W/ ARGILLITIC INCLUSIONS FRACTURED, 10% QTZ / CARB AS FRACTURE FILLS - CATACLASTIC ZONE							
41.76	43.00	50°	ARGILLITE 2% QTZ, CARB RANDOM ORIENT. CONTACT W/ DK GN VOLCANICS 42.13-43.0 LG LAPILLI SIZE VOLCANIC FRAGS							
43.0	51.01		LIGHT GRAY / GREEN VOLCANICS APHANITIC TEXTURE W/ MINOR ARGILLITIC INCLUSIONS - CARBONATE VEINING PERVIOUSIVE (10%) 48.30-50.40 FLOW DK GN VOLCANICS CHLORITIC / MINOR ARGILLITE INCL. TR PY							

DEPTH		LOG	DESCRIPTION	Sample No.	FROM	TO	CORE INT.	SAMP INT.	Au	Au	GLOB- Sheet	25 2
FROM	TO								ppm	oz/t		
			51.13 - 51.23 QTZ/CARB VEIN (CALC. RICH) 60° to CA						9/G		As ppm	
51.01	51.75		ARGILLITE/CHERT LG 7 10MM VOLCANIC INCLUSIONS CARBONATE RICH									
51.75	52.75		TAN ALTERED VOLCANIC (ANKERITE) BRECCIATED SM to LG. LAPILLI SIZE FRAGS IN ARGILLITIC MATRIX, 5% QTZ CARB 50° CONTACT w/ ARGILLITE - 51.75 1% PY AS FINE GRAINED DISSEMINATIONS	143642	52.40	53.10	0.7	0.7	4.003		25	
52.75	66.50		ARGILLITE VOLCANICS - CARBONATE RICH (10%) SOME MED GRAY BANDING COARSE GRAINED 59.33 - 59.36 QTZ CARB VEIN 50° to CA TR DISS. PY PERVASIVE	143688	66.44	67.50	1.06	1.06	3.80		8795	
66.50	67.28		TAN ALTERED VOLCANICS w/ ARGILLITE ANKERITIC ALTIN, SOFT 2-3% DISS PY									
67.28	71.26		ARGILLITE MIXED w/ DK VOLCANIC - COARSE GRAINED 5% QTZ CARB RANDOM ORIENT									
71.26	72.54		TAN ALTERED VOLCANIC - ANKERITIC FRACTURED w/ SM FLOWS 5% QTZ/CARB 3-5% PY AS VEINLETS / FRACTURE FILLS	143634 143640 143641	71.0 72.0 73.0	71.75 73.0 73.5	0.75 1.0 0.5	0.75 1.0 0.5	2.3E 0.03 4.003		71000 515 25	









DEPTH			LOG	DESCRIPTION	Sample No.	FROM	TO	CORE INT.	SAMP INT.	Au	Au	As
FROM	TO	INT.										
0.0	16.72			CASING & OUBURDEN								
16.72	64.52			LIGHT TO DARK GREEN/MAROON VOLCANICS - ARGILLICALLY ALTERED (SERPENTINIC TALC -ACTION) BRITTLE/FRACTURED FLOWS 10-12% QTZ/CARBONATE PERVASIVE - RANDOM STRINGERS, TR PY	143693	60.4	61.4	1.0	1.0	915		25
				13.72-28.83 - DR GN VOLCANIC ARGILLITIC ALTERATION, FRACTURED, CALCAREOUS, CHLORITIC 23.47-23.60 SM FAULT								
			RQ	25% ≥ 10CM								
				28.83-32.61 - MAROON VOLCANICS - HEMATITE STAINING, CHLORITIC, TALC ALT'N								
				39.26-34.36 QTZ CARB. VEIN 50° to CA								
				36.86-37.06 SM. FLOW, FRAGS (≥ 2MM) TR PY								
			65°	44.13-44.25 - VOLCANIC FLOW CONTACT								
			67°	46.20-46.30 - SM. DYKE - POLYLYTHIC 52.70-52.90 SM SHEAR								
				52.90-64.52 ARGILLITE CHLORITIC, TALC ALTERED; HEMATITE, 10% QTZ/CARB, TR PY								
			RQ	(60 ≥ 10CM)								

DRILL HOLE RECORD			CLAIM	BEARING	DIP	SURVEY TYPE	CORE SIZE: NQ	HOLE # LZ-06-02
COMPANY: LEVON RESOURCES LTD			LOCATION	COLLAR	90°	45°	sin	STARTED: 18/10/06 SHEET: 1 of 2
PROJECT: CONGRESS - LOU ZONE			ELEVATION 795 M					COMPLETED: 20/10/06 FINAL DEPTH: 117.96
UNITS Metric			LATITUDE 5639045 N					LOGGED BY: CK
			DEPARTURE 514861 E					





DEPTH			LOG	DESCRIPTION	Sample No.	FROM	TO	CORE INT.	SAMP INT.	Au <del>GR</del>	Au oz./t	As ppm
FROM	TO											
0.0	4.17			CASING & OVERBURDEN								
5.18	52.82			DARK GREEN / MAROON VOLCANICS (ASALT)								
				FRACTURED, BROKEN, FAIR TO POOR CORE RECOVERY, QTZ-CARB. VEINING PERVASIVE	143687	26.5	27.5	1.0	1.0	0.01		<5
				GRAPHIC ARG. INCLUSIONS, CALCAREOUS, CHLORITIC	143698	37.0	38.0	1.0	1.0	0.01		<5
			RQ	5.18-17.60, VERY POOR RECOVERY								
				10% ≥ 10 CM								
				17.60-20.42 FAULT, RUBBLE								
				26.75-27.45 - MEDIUM GREEN VOLCANIC, FINE GRAINED CHLORITIC, TR PY								
				29.57-32.00 - FAULT, RUBBLY CORE								
			RQ	25% $\geq$ 10 CM								
				34.91-37.63 - MAROON VOLCANIC, BROKEN FRACTURED, QTZ/CARB VEINING ( $\geq$ 20 MM)								
				AS FRACTURE FILLS, LOCALLY CHLORITIZED HEMATITE, TR-1% PY								
				37.63-38.13, AMYG. FLOW, LIGHT GREEN								
				45% to CA								
				39.13-39.43 BROWN FLOW SM TO LG FLOWS (2MM TO 7MM) MINOR FLOW BANDING, DARK ARG. MATRIX, CALCAREOUS								

DRILL HOLE RECORD

CLAIM	LOCATION	COLLAR	BEARING	DIP	SURVEY TYPE	CORE SIZE: NO	HOLE # L2-06-03
COMPANY: LEVON RESOURCES LTD	ELEVATION 385 M		90°	-45°	STN	STARTED: 7/11/06	SHEET: 1 of 5
PROJECT: CONGRESS - LOU ZONE	LATITUDE 563829 N					COMPLETED: 8/11/06	FINAL DEPTH: 203.30
UNITS Metric	DEPARTURE 514764 E					LOGGED BY: CK	

415





9/5

DEPTH		LOG	DESCRIPTION	Sample No.	FROM	TO	CORE INT.	SAMP INT.	Au	Au	LZ06-03
FROM	TO								g/t	oz./t	Sheet: 4
			148.30 - 148.94 LIGHT GRAY ALTERATION (ANKERITIC <sup>3</sup> )								As ppm
		90°	TRANSITION TO TAN VOLCANICS								
148.94	154.57		TAN ALTERED VOLCANIC DYKE, FRACTURED								
			FLOW, ANKERITIC ALT'N, SOFT, FRAG. UP TO	143709	150.0	151.0	1.0	1.0	5.41		538
			10MM, 3-5% PY AS FRACTURE FILLS +	143710	151.0	152.0	1.0	1.0	3.39		1793
			VEINLETS, TR ARP,	143711	152.0	153.0	1.0	1.0	0.08		366
			153.13 - 153.37 LG ≥ 5MM CALC. PHENOCRYSTS	143712	153.0	154.0	1.0	1.0	0.03		235
			153.40 - 154.57 MINGR FLOW BANDING, DK	143713	154.0	155.0	1.0	1.0	0.05		357
			MATRIX, 2% CARB. VEINING, LG (≥ 5MM) QTZ	143714	155.0	156.0	1.0	1.0	<0.01		8
			FRAGS								
154.57	155.24	45°	TRANSITION TO TAN ALTERED FELDSPAR PORPH.								
			DYKE, 15% WHITE PHENOS, TAN MATRIX								
			1-2% DISS PY								
155.24	166.61		FELDSPAR PORPHYRY 25% WHITE PHENOS,	143715	166.50	167.50	1.0	1.0	<0.01		5
			DK GRAY MATRIX, CALCAREOUS, SLIGHT	143716	167.50	168.50	1.0	1.0	<0.01		25
			K-SPAR ALT'N, MINGR HEMATITE								
			162.46 - 163.22 QTZ/CARB VEINING								
			PERVASIVE, RANDOM ORIENTATIONS								
		RQ	50% ± 10CM								
166.61	167.39		ALTERED FELDSPAR PORPHYRY DYKE, TAN								
			COLORED 30% WHITE PHENOS, BLEACHED								
167.39	169.86		LG BRECCIA FRAGS (≥ 5CM)								
169.86	177.16		FELDSPAR PORPHYRY, 25% WHITE PHENOCRYSTS	143717	173.50	174.50	1.0	1.0	0.07		305
			DARK GRAY MATRIX 5% QTZ CARB	143718	174.50	175.00	0.5	0.5	<0.01		6
			VEINING / STRINGERS 5M (≥ 2MM)	143719	177.0	178.0	1.0	1.0	0.30		726
			173.64 - 174.0 CHALKY, GOUGE, TR PY	143720	178.0	179.0	1.0	1.0	1.90		4767



DEPTH			LOG	DESCRIPTION	Sample No.	FROM	TO	CORE INT.	SAMP INT.	Au oz./t	Au oz./t
FROM	TO										
0.0	1.0			CASING							
1.54	26.47			DARK GREEN / MAROON VOLCANICS FRACTURED / FLOWS, FINE GRAINED (0.5 MMS) CALCAREOUS, 5% QTZ / CARB VEINING LOCALLY CHLORITIZED, ARGILLIC, ALT'N / SERPENTINE? 4.50 - 6.50 BRACCIATED, LAPILLI SIZE FRAGS, DK ARGILLIC MATRIX							
		40°		15.83 - 16.23 QTZ / CARB FLOODING							
				18.78 - 18.87 QTZ / CARB VEIN 45° TO CA							
		R9		30° ≥ 10 CM FAIR RECOVERY							
26.47	29.57	40°		FELDSPAR PORPHYR; DYKE 10% WHITE PHENOCRYSTS (≥ 2MM) / DK GRAY MATRIX, MINOR CARBONATE VEINING							
29.57	41.76			DARK GREEN / MAROON VOLCANICS, FRACTURED, FLOWS, LOCALLY BRACCIATED, CALCAREOUS, SERP. 5-10% QTZ CARB VEINS / STRINGERS RANDOM ORIENTATIONS, ARG. ALT'N 35.66 - 39.71 BROKEN RUBBLY CORE							
		R9		25% ≥ 10 CM POOR RECOVERY							
41.76	42.61	35°		PORPHYRITIC DYKE 5% WHITE PHENOS (≥ 2MM) LIGHT GREEN MATRIX, HEMATITE STAINED,							

DRILL HOLE RECORD			CLAIM	BEARING	DIP	SURVEY TYPE	CORE SIZE: NQ	HOLE # LZ-06-04	
COMPANY: LEVON RESOURCES LTD			LOCATION	30°	-45°	sta	STARTED: 11/11/06	SHEET: 1 of 3	
PROJECT: CONGRESS - LOU ZONE			ELEVATION 983 M				COLLAR	COMPLETED: 3/1/07	FINAL DEPTH: 57.02
UNITS Metric			LATITUDE 5638227 N				DEPARTURE 514760 E	LOGGED BY: CK	







DEPTH			LOG	DESCRIPTION	Sample No.	FROM	TO	CORE INT.	SAMP INT.	Au oz./ft	Au oz./ft		
FROM	TO												
0.0	4.57			CASING									
4.57	47.85			MARON/MED GREEN VOLCANICS, FINE GRAINED, SEARED, CALCAREOUS, 10% QTZ CARB. AS VEINLETS/STRINGERS, SERP/TNC ALT'N									
			RQ	4.57-23.00 - POOR RECOVERY (90% 10CM)									
				9.10 - 9.47 QTZ CARB VEIN 30° TO CA									
			25°	14.73 - 14.94 - MED. GN VOLCANICS CONTACT CHLORITIC,									
				24.74 - 28.55 - LIGHT GN VOLCANIC FLOW FINE GRAINED, FRACTURED - LAPILLI SIZE FRAGS DK MATRIX, 5% QTZ/CARB VEINLETS, TR PY									
				29.37 - 32.00 - SAME DESCRIPTION AS ABOVE EXCEPT MARON VOLC FRAGS									
				33.42 - 39.47 QTZ/CARB VEIN 50° TO CA									
				44.81 - 47.85 - SHEAR ZONE, BROKEN SHATTERED CORE, GOUGE									
			RQ	POOR RECOVERY (30% 10CM)									
47.85	50.04			ARGILLIC FLOW W/ LIGHT GN VOLCANIC INCLUSION, 5% QTZ CARB MICROZIMM/VEINLETS									
				47.85 - 48.04 SOFT GOUGE									

DRILL HOLE RECORD				CLAM	BEARING	DIP	SURVEY TYPE	CORE SIZE: NQ	HOLE # LZ-06-05	
COMPANY: LEVON RESOURCES LTD				LOCATION	90°	-55°	str	STARTED: 4/11/06	SHEET: 1 of 4	
PROJECT: CONGRESS - LOU ZONE				ELEVATION 942 M				COLLAR	COMPLETED:	FINAL DEPTH: 185.01
UNITS Metric				LATITUDE 5638124 N				DEPARTURE 514759 E	LOGGED BY: CK	



9/15

DEPTH		LOG	DESCRIPTION	Sample No.	FROM	TO	CORE INT.	SAMP INT.	Au	Au	GLOB- Sheet:	CS
FROM	TO								<del>ppm</del>	oz/t		
97.98	100.07	50°	CHERT/ARGILLITE, BRECCIATED 15% QTZ/CARB VEINING AS FRACTURE FILLS									As ppm
100.07	115.81		MED GREEN VOLCANICS - FINE TO MED. GRAINED, FRACTURED/FLOWS 10% QTZ/CARB VEINING AS FRACTURE FILLS & STRINGERS, MINOR ARGILLIC INCLUSIONS LOCALLY SERPENTINIZED (TALC) 103.96-104.09 - QTZ/CARB VEIN 40° to CA									
		RD	110.15-115.24 FAIR RECOVERY (50% ≥ 10cm) 20% QTZ/CARB VEINING RANDOM ORIENTATIONS									
115.81	131.87	45°	CHERT/ARGILLITE - BRITTLE/FRACTURED 15% QTZ/CARB VEINING (MICRO ≤ 1MM to LG ≥ 20MM) LOCALLY BRECCIATED, SOME VOLCANIC INCLUSIONS 122.24-127.6 LG ≥ 5MM MED GREEN VOLCANIC INCLUSIONS 128.81-131.87 - BRECCIATED ARGILLITE, QTZ VEINING AS FRACTURE FILLS, 1-2% PY AS DISSEM. & VEINLETS									
131.87	133.43	25°	TAN ALTERED VOLCANIC DYKE, FRACTURED, 5-10MM TO LAPILLI SIZE FRAGS FINE GRAINED, 5% PY AS FRACTURE FILLS & VEINLETS TO ARPY	14376	131.0	132.0	1.0	1.0	0.14			96
				143762	132.0	133.0	1.0	1.0	4.21			2258
				143763	133.0	134.0	1.0	1.0	0.30			1445



DEPTH		LOG	DESCRIPTION	Sample No.	FROM	TO	CORE INT.	SAMP INT.	Au	Au	As
FROM	TO										
DRILL HOLE RECORD											
COMPANY: LEVON RESOURCES LTD			CLAIM LOCATION	COLLAR	BEARING	DIP	SURVEY TYPE	CORE SIZE: NQ	HOLE # LZ-08-06		
PROJECT: CONGRESS - LOU ZONE			ELEVATION 910 M		96°	-45°	str	STARTED:	SHEET: -1 of 4		
UNITS Metric			LATITUDE 5638076 N					COMPLETED:	FINAL DEPTH: 194.16		
			DEPARTURE 514753 E					LOGGED BY: CK	915		
0.0	6.10		CASING & OUBURDEN								
6.10	53.95		MAROON/GREEN VOLCANICS - FINE GRAINED, FRACTURED/FLOWS, 10% QTZ CARB. LOCALLY SERPENTINIZED, MINOR TAN ALTERED VOLCANIC INCLUSIONS								
		RR	17.37-20.42 FAULT, BROKEN RUBBLE, CORE LOSS - 22.48 10% ≥ CM POOR RECOVERY								
			22.48-23.72 - LIGHT GREEN VOLCANICS, MAROON VOLC. FLOW 25.17-25.26 GRAPHIC ARG. TR. DIBS, PY 25.30-25.32 QTZ CARB VEIN 70° TO CA 36.36-37.20 - CORE LOSS, BROKEN SHATTERED								
		25'	41.68-41.76 - GRAPHIC ARGILLITE								
		40'	41.76-42.03 - QTZ/CARB ELUDDING TR. PY 50.45-51.59 - MED GRAY VOLCANIC, FINE GR, SM ≥ 1MM CALCITE VEINING								
53.95	57.00	RR	TRANSITION TO FELDSPAR PORPHYRY DYKE POOR RECOVERY 20% ≥ 10 CM								
57.0	79.65		FELDSPAR PORPHYRY DYKE 25% WHITE PHENOCRYSTS UP TO 1CM, DARK TO LIGHT GR	14370	64.0	65.0	1.0	1.0	<0.01		<5
			MATRIX MINOR CALCITE VEINING (SM ≥ 1MM), S	14371	65.0	66.0	1.0	1.0	<0.01		<5
				14372	71.0	72.0	1.0	1.0	<0.01		<5



9/8 LZ-06-06

DEPTH		LOG	DESCRIPTION	Sample No	FROM	TO	CORE INT.	SAMP INT.	Au	Au	Sheet: 53	
FROM	TO								oz./ft.	oz./ft.		
125.70	127.54		LIGHT GN VOLCANIC, FINE GRAINED POLYLITHIC TUFF, MINOR QTZ/CARB VEINING TRANSITION TO TAN ALTERED VOLCANIC								As ppm	
128.54	132.50	20'	TAN ALTERED VOLCANICS, BRECCIATED MINOR ARG/CHERT INCLUSIONS, 5% QTZ/ CARB VEINING RANDOM ORIENTATIONS 5% PY, TR-1% ARSP AS FRACTURE FILLS & VEINLETS 129.72-132.50 LAPILLI SIZE FRAGS 5% PY, 1% ARSP	143786 143787 143788 143789 143790 143791 143792	128.5 129.5 130.5 131.5 132.5 133.5 134.5	129.5 130.5 131.5 132.5 133.5 134.5 135.5	1.0 1.0 1.0 1.0 1.0 1.0 1.0	1.0 1.0 1.0 1.0 1.0 1.0 1.0	0.29 0.11 0.17 0.03 0.01 0.01 0.01		767 1164 731 664 21 41 93	
		RQ	85% $\frac{7}{10}$ CM	143793	136.5	136.5	1.0	1.0	<0.01			12
132.50	145.80		CHERT/ARCHELITE W/ VOLCANIC INCLUSIONS BRECCIATED 5% QTZ/CARB VEINING +2% FINELY DISS PY 136.92-142.50 TAN/GN VOLCANIC INCLUSIONS - LAPILLI SIZE 5% QTZ VEINING, 2-3% PY, TR ARSPY 145.40-145.80 BRECCIA FLOW / ARG. MATRIX	143794 143795 143796 143797 143798 143799 143800	136.5 137.5 138.5 139.5 140.5 141.5 142.5	137.5 138.5 139.5 140.5 141.5 142.5 143.5	1.0 1.0 1.0 1.0 1.0 1.0 1.0	1.0 1.0 1.0 1.0 1.0 1.0 1.0	<0.01 0.01 0.01 0.02 2.01 0.01			8 10 10 8 25 17 16
145.80	155.43	30'	TAN ALTERED VOLCANICS W/ CHERT/ARG INCLUSIONS, FINE GRAINED, 5% QTZ CARB VEINING, VARIOUS ORIENTATIONS 150.9-155.43 BRECCIATED, 5% PY AS FRACTURE FILLS + VEINLETS, TR-1% ARSPY	143801 143802 143803 143804 143805 143806 143807	143.5 144.5 145.5 146.5 147.5 148.5 149.5	144.5 145.5 146.5 147.5 148.5 149.5 150.5	1.0 1.0 1.0 1.0 1.0 1.0 1.0	1.0 1.0 1.0 1.0 1.0 1.0 1.0	<0.01 0.53 1.08 0.01 0.01 0.02 0.01			25 357 318 8 25 128 145
155.43	194.16		MARON/GREEN VOLCANICS - FINE GRAINED FRACTURED/BRECCIATED/FLOWS 15% QTZ CARB VEINING - 168.91-169.30 GOUGE, MINOR ALT N (ANKHYME) 181.97-182.80 LAPILLI SIZE FRAGS IN BLACK MATRIX	143808 143809 143810 143811	150.5 151.5 152.5 153.5	151.5 152.5 153.5 154.5	1.0 1.0 1.0 1.0	1.0 1.0 1.0 1.0	<0.01 4.23 1.64 0.01			24 3604 3175 52









9/15

DEPTH		LOG	DESCRIPTION	Sample No.	FROM	TO	CORE INT.	SAMP INT.	Au	Au	LZ06-07	Sheet: 3/AS
FROM	TO								ppm	oz./t		
134.83	137.91		MARCON VOLCANIC - FRACTURED 5% QTZ	143831	120.0	121.0	1.0	1.0	<0.01			5
			VEINLETS / STRINGERS KEMATITE	143832	121.0	122.0	1.0	1.0	<0.01			9
			136.25 - 136.42 - 2.5% PY AS DISSEM.	143833	122.0	123.0	1.0	1.0	<0.01			7
				143834	123.0	124.0	1.0	1.0	<0.01			10
137.91	140.07		TAN ALTERED VOLCANICS / MARCON VOLC.	143835	124.0	125.0	1.0	1.0	<0.01			10
			BRECCIATED 5% QTZ VEINING RANDOM	143836	125.0	126.0	1.0	1.0	<0.01			10
			TR- 1% FINELY DISS PY	143837	126.0	127.0	1.0	1.0	<0.01			11
				143838	127.0	128.0	1.0	1.0	<0.01			12
140.07	148.97		CHERT / ARGILLITE - SILICEOUS 10% QTZ	143839	128.0	129.0	1.0	1.0	<0.01			12
			VEINING / STRINGERS POLYLITHIC INCLUSIONS	143840	129.0	130.0	1.0	1.0	<0.01			33
			TR- 1% FINELY DISS PY									
			HT. 93- 147.86 - TAN ALTERED VOLCANIC	143841	130.0	131.0	1.0	1.0	<0.01			19
			INCLUSIONS	143842	131.0	132.0	1.0	1.0	0.03			33
				143843	132.0	133.0	1.0	1.0	0.02			128
148.97	155.40	20°	FELDSPAR PORPHYRY DYKE 15% WHITE	143844	133.0	134.0	1.0	1.0	1.64			1348
			PHENOCRYSTS, DARK GRAY MATRIX, MINOR	143845	134.0	135.0	1.0	1.0	0.18			112
			FRACTURETING, MINOR > 2MM CALCITE	143846	135.0	136.0	1.0	1.0	<0.01			7
			VEINING	143847	136.0	137.0	1.0	1.0	<0.01			8
			154.49 - 155.40 TAN ALTERED FELDSPAR	143848	137.0	138.0	1.0	1.0	<0.01			104
			PORPHYRY, MINOR CALCITE TR-1% DISS PY	143849	138.0	139.0	1.0	1.0	0.43			2863
				143850	139.0	140.0	1.0	1.0	<0.01			10
155.40	156.24	22°	CHERT / ARGILLITE - SILICEOUS, MINOR CARB.									
			BRECCIATED W/ VOLCANIC INCLUSIONS									
			TR- 1% FINELY DISS PY	143851	148.0	149.0	1.0	1.0	0.06			713
				143852	155.0	156.0	1.0	1.0	9.96			5575
156.24	156.48		FELDSPAR PORPHYRY - BLEACHED / ALTERED	143853	156.0	157.0	1.0	1.0	4.85			2996
			TR. DISS PY	143854	157.0	157.1	1.0	1.0	7.02			3377
156.68	157.86		CHERT / ARGILLITE SILICEOUS, BRECCIATED									
			MINOR VOLC INCLUSIONS TR DISS PY									

ppm

CHECK

















DRILL HOLE RECORD		CLAIM		BEARING	DIP	SURVEY TYPE	CORE SIZE: NQ	HOLE # C-06-01
COMPANY: LEVON RESOURCES LTD		LOCATION	COLLAR	100°	-45°	STN	STARTED: 25/11/06	SHEET: 1 of 3
PROJECT: CONGRESS - HOWARD		ELEVATION					COMPLETED:	FINAL DEPTH: 151.51
UNITS Metric		LATITUDE N					LOGGED BY: Ck	
		DEPARTURE E						

DEPTH		LOG	DESCRIPTION	Sample No.	FROM	TO	CORE INT.	SAMP INT.	Au oz./t	Au oz./t
FROM	TO									
0.0	4.70		CASING + OVERBURDEN							
4.70	33.32		MED GREEN/MARON VOLCANICS - FINE GRAINED, FRACTURED / MINOR FLOWS, CALCAREOUS 15% CARB VEINING - RANDOM ORIENTATIONS, LOCALLY HEMATITIC, CHLORITIC 14.23 - 14.57 - FAULT, RUBBLY CORE							
		20°	17.14 - 20.42 GABBRO DYKE W/ YDC INCLUSIONS							
			20.94 - 21.02 - QTZ/CARB VEIN 95° TO CA							
			21.48 - 21.53 - APLITE IN QTZ/CARB TR PY AS FINE DKS							
			22.52 - 31.14 - PRECIPITATED - QTZ/CARB AS FRACTURE FILLS, HEMATITIZED							
33.32	33.77		CALL MARGIN							
33.77	50.37	35°	GABBRO/DIORITE DYKE - MED GRAINED, SOFT CHLORITE, BIOTITE, 5% CARB VEINING 41.76 - 43.21 - HEMATITIZED GABBRO (CHLORITIC) SOFT TR OBS PY							
50.37	60.40		DK GREEN VOLCANIC, FINE GR, FRACTURED, LOCALLY SERPENTINIZED, CHLORITIC, SOFT							
		RQ	60% 7 10' CM							





DEPTH			LOG	DESCRIPTION	Sample No.	FROM	TO	CORE INT.	SAMP INT.	Au g/g	Au oz/t	As ppm
FROM	TO											
0.0	9.14			CASING / OVERBURDEN						915		
9.14	38.56			MED. GREY / MAROON VOLCANOS - FINE GRAINED, FRACTURED / BROKEN MINOR CARB VEINING 1% MICRO VEINS, LOCALLY SHEARED, CHLORITIC, SERPENTINIZED	143918	8.5	9.5	1.0	1.0	<0.01		<5
				9.14 - 14.53 FAIR RECOVERY	143919	18.5	19.5	1.0	1.0	2.001		<5
		29		40% > 10 CM	143920	19.5	20.5	1.0	1.0	0.9		<5
				17.07 - 17.21 - GRAPHITIC ARGILLITE	143921	23.0	24.0	1.0	1.0	<0.01		<5
		15		19.07 - 22.64 - MAROON VOLC. HEMATITIC, MINOR QTZ CARB VEINETS - RANDOM ORIENT.	143922	24.0	25.0	1.0	1.0	<0.01		<5
				26.17 - 27.22 MED GREEN VOLC. FINE GRAINED BRECC., ARG MATRIX, TR PY AS DISSEM. & FLEBS	143923	25.0	26.0	1.0	1.0	<0.01		<5
				26.17 - 27.22 MED GREEN VOLC. FINE GRAINED BRECC., ARG MATRIX, TR PY AS DISSEM. & FLEBS	143924	26.0	27.0	1.0	1.0	<0.01		<5
				22.64 - 35.66 - MAROON VOLC., MINOR QTZ VEINING	143925	30.0	31.0	1.0	1.0	<0.01		<5
		35		35.66 - 36.07 BROKEN / SMATTERED CORE FAULT	143926	35.0	36.0	1.0	1.0	<0.01		<5
					143927	47.5	48.5	1.0	1.0	<0.01		<5
					143928	56.0	57.0	1.0	1.0	<0.01		<5
					143929	60.0	61.0	1.0	1.0	<0.01		<5
36.56	61.13		30	FELSIC PORPHYRY DYKE - 30% WHITE CHENCRISTS (UP TO 1CM) NED GREY MATRIX MINOR QTZ CARB VEINING	143930	74.0	75.0	1.0	1.0	<0.01		<5
				50.22 - 51.30 - TAN ALTERED VOLC. BRECCIATED 2-3% PY AS VEINETS	143931	81.0	82.0	1.0	1.0	<0.01		<5
					143932	87.0	88.0	1.0	1.0	<0.01		<5

DRILL HOLE RECORD				CLAIM	BEARING	DP	SURVEY TYPE	CORE SIZE: NQ	HOLE # C-06-02
COMPANY: LEVON RESOURCES LTD				LOCATION	COLLAR	90°	STN	STARTED: 29/11	SHEET: 1 of 3
PROJECT: CONGRESS - JERARD				ELEVATION		-55°		COMPLETED:	FINAL DEPTH: 159.39
UNITS Metric 12				LATITUDE	N			LOGGED BY: CK.	
				DEPARTURE	E				







## **Appendix C**

### **Assay Results and Assay Procedure**

## GOLD AND PRECIOUS METALS ANALYSIS

### Fire Assay

This is the most commonly used method where precision of results is a high priority, including virtually all drilling samples. Samples are diluted to a larger volume (if they are to be read on the AA), and all high grade samples are automatically finished gravimetrically.

Description	Det. Limit
1/2 Assay ton FA, AA/Grav finish	0.01 g/tonne
1 Assay ton FA, AA/Grav finish	0.01 g/tonne
2 Assay ton FA, AA/Grav finish	0.01 g/tonne

## MULTI-ELEMENT ICP ANALYSIS

### Trace Metal Analysis by ICP-AES

#### a. Aqua Regia Leach / ICP-AES

Concentrated hydrochloric (HCl) and nitric (HNO<sub>3</sub>) acids are used to dissolve most base metals and pathfinder elements. Dissolution may not be complete for elements marked with an asterisk (\*).

#### b. Multi Acid Leach / ICP-AES

Total digestion using hydrochloric (HCl), hydrofluoric (HF), nitric (HNO<sub>3</sub>) and perchloric (HClO<sub>4</sub>) acids. This strong acid combination will attack many mineral types that are not completely dissolved with Aqua Regia. Dissolution may not be complete for Ba and Mg. Some loss of Al and Mn may occur.(t)

Element	Detection Limit		Upper Limit
	Aqua Regia	Multi-Acid	
Al *†	0.01%	0.01%	15%
Sb	5 ppm	-	10000 ppm
As	5 ppm	-	10000 ppm
Ba *†	10 ppm	10 ppm	10000 ppm
Be *	0.5 ppm	0.5 ppm	100 ppm
Bi	5 ppm	5 ppm	10000 ppm
Cd	1 ppm	1 ppm	100 ppm
Ca *	0.01%	0.01%	15%
Cr *	1 ppm	1 ppm	10000 ppm
Co	1 ppm	1 ppm	10000 ppm
Cu	1 ppm	1 ppm	10000 ppm
Fe *	0.01%	0.01%	15%
Pb	2 ppm	2 ppm	10000 ppm
Mg *†	0.01%	0.01%	15%
Mn *†	5 ppm	5 ppm	10000 ppm

Element	Detection Limit		Upper Limit
	Aqua Regia	Multi-Acid	
Mo	2 ppm	2 ppm	10000 ppm
Ni	1 ppm	1 ppm	10000 ppm
P *	10 ppm	10 ppm	10000 ppm
K *	0.01%	0.01%	10%
Sc	1 ppm	-	10000 ppm
Ag	0.2 ppm	1 ppm	200 ppm
Na *	0.01%	0.01%	5%
Sr *	1 ppm	1 ppm	10000 ppm
Sn *	10 ppm	-	1000 ppm
Ti *	0.01%	0.01%	10%
W *	10 ppm	10 ppm	10000 ppm
V	1 ppm	1 ppm	10000 ppm
Y	1 ppm	-	10000 ppm
Zn	1 ppm	2 ppm	10000 ppm
Zr *	1 ppm	-	10000 ppm

# CERTIFICATE OF ASSAY AK 2006-1857

---

**LEVON RESOURCES LTD.**  
Suite 400-455 Granville Street  
**Vancouver, BC**  
V6C 1T1

3-Dec-06

*No. of samples received: 78*  
*Sample Type: Core*  
*Project #: GL 06-01*  
*Submitted by: Curt Kauss*

ET #.	Tag #	Au (g/t)	Au (oz/t)
1	143501	<0.03	<0.001
2	143502	<0.03	<0.001
3	143503	<0.03	<0.001
4	143504	<0.03	<0.001
5	143505	<0.03	<0.001
6	143506	<0.03	<0.001
7	143507	<0.03	<0.001
8	143508	<0.03	<0.001
9	143509	<0.03	<0.001
10	143510	<0.03	<0.001
11	143511	3.68	0.107
12	143512	<0.03	<0.001
13	143513	<0.03	<0.001
14	143514	<0.03	<0.001
15	143515	<0.03	<0.001
16	143516	3.30	0.096
17	143517	8.45	0.246
18	143518	7.49	0.218
19	143519	<0.03	<0.001
20	143520	<0.03	<0.001
21	143521	<0.03	<0.001
22	143522	<0.03	<0.001
23	143523	<0.03	<0.001
24	143524	0.03	0.001
25	143525	<0.03	<0.001

*GL-06-01*

---

**ECO TECH LABORATORY LTD.**  
Jutta Jealouse  
B.C. Certified Assayer

ET #.	Tag #	Au (g/t)	Au (oz/t)
26	143526	<0.03	<0.001
27	143527	<0.03	<0.001
28	143528	0.03	0.001
29	143529	<0.03	<0.001
30	143530	<0.03	<0.001
31	143531	<0.03	<0.001
32	143532	0.05	0.001
33	143533	1.13	0.033
34	143534	4.57	0.133
35	143535	3.76	0.110
36	143536	0.14	0.004
37	143537	0.39	0.011
38	143538	0.04	0.001
39	143539	0.55	0.016
40	143540	<0.03	<0.001
41	143541	<0.03	<0.001
42	143542	<0.03	<0.001
43	143543	<0.03	<0.001
44	143544	<0.03	<0.001
45	143545	<0.03	<0.001
46	143546	<0.03	<0.001
47	143547	<0.03	<0.001
48	143548	<0.03	<0.001
49	143549	<0.03	<0.001
50	143550	0.41	0.012
51	143551	0.31	0.009
52	143552	<0.03	<0.001
53	143553	<0.03	<0.001
54	143554	<0.03	<0.001
55	143555	<0.03	<0.001
56	143556	0.24	0.007
57	143557	<0.03	<0.001
58	143558	<0.03	<0.001
59	143559	<0.03	<0.001
60	143560	<0.03	<0.001
61	143561	0.06	0.002
62	143562	4.63	0.135
63	143563	4.79	0.140
64	143564	0.16	0.005
65	143565	<0.03	<0.001
66	143566	0.03	0.001

G1-06-01

**ECO TECH LABORATORY LTD.**  
Jutta Jealouse  
B.C. Certified Assayer

ET #.	Tag #	Au (g/t)	Au (oz/t)
67	143567	<0.03	<0.001
68	143568	<0.03	<0.001
69	143569	<0.03	<0.001
70	143570	<0.03	<0.001
71	143571	<0.03	<0.001
72	143572	<0.03	<0.001
73	143573	<0.03	<0.001
74	143574	<0.03	<0.001
75	143575	0.18	0.005
76	143576	0.13	0.004
77	143577	<0.03	<0.001
78	143578	<0.03	<0.001

GL-06-01

**QC DATA:**

**Repeat:**

1	143501	<0.03	<0.001
10	143510	<0.03	<0.001
11	143511	3.67	0.107
16	143516	3.46	0.101
17	143517	8.83	0.258
18	143518	7.85	0.229
19	143519	<0.03	<0.001
33	143533	1.07	0.031
34	143534	5.29	0.154
35	143535	4.06	0.118
36	143536	0.14	0.004
39	143539	0.62	0.018
45	143545	<0.03	<0.001
50	143550	0.43	0.013
51	143551	0.39	0.011
54	143554	<0.03	<0.001
62	143562	5.03	0.147
63	143563	4.94	0.144

**Resplit:**

1	143501	<0.03	<0.001
36	143536	0.20	0.006

**Standard:**

OXE42	0.59	0.017
OXE42	0.61	0.018
OXE42	0.60	0.017

ECO TECH LABORATORY LTD.  
1041 Dallas Drive  
AMLOOPS, B.C.  
V6C 6T4

## ICP CERTIFICATE OF ANALYSIS AK 2006-1857

LEVON RESOURCES LTD.  
Suite 400-455 Granville Street  
Vancouver, BC  
V6C 1T1

Phone: 250-573-5700  
Fax: 250-573-4557

No. of samples received: 78  
Sample Type: Core  
Project #: GL 06-01  
Submitted by: Curt Kauss

Values in ppm unless otherwise reported

Et #.	Tag #	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Tl %	U	V	W	Y	Zn
1	143501	<0.2	3.91	<5	85	10	5.74	<1	45	180	51	7.66	20	4.34	1498	5	0.07	141	1680	40	<5	<20	110	0.02	<10	147	<10	22	85
2	143502	<0.2	3.62	5	80	10	5.63	<1	44	192	50	7.21	20	3.92	1315	3	0.06	131	1670	38	<5	<20	116	0.04	<10	155	<10	24	84
3	143503	<0.2	4.44	5	75	5	6.03	<1	52	145	60	7.71	20	4.51	1506	<1	0.16	99	1090	42	<5	<20	199	0.22	<10	170	<10	37	83
4	143504	<0.2	3.20	<5	310	5	7.26	<1	38	112	48	5.76	10	3.53	1220	1	0.17	75	800	30	<5	<20	189	0.06	<10	131	<10	24	63
5	143505	<0.2	2.40	<5	290	10	8.82	<1	37	113	43	5.60	10	2.67	1071	1	0.08	76	860	26	<5	<20	201	0.06	<10	146	<10	26	61
6	143506	<0.2	0.54	5	70	<5	4.87	<1	41	75	49	5.92	<10	2.31	1118	4	0.03	89	1400	4	40	<20	43	<0.01	<10	124	<10	21	70
7	143507	<0.2	0.50	10	70	5	5.96	<1	46	84	48	6.21	<10	2.85	1170	5	0.03	88	840	2	40	<20	36	<0.01	<10	144	<10	19	67
8	143508	<0.2	0.45	15	70	5	6.01	<1	40	68	45	6.43	<10	2.94	1407	5	0.02	76	740	<2	40	<20	37	<0.01	<10	139	<10	16	81
9	143509	<0.2	0.51	25	65	<5	6.02	<1	38	67	46	6.06	<10	2.83	1230	5	0.02	67	760	<2	45	<20	40	<0.01	<10	119	<10	15	66
10	143510	<0.2	0.44	430	55	5	5.70	<1	41	34	43	6.14	<10	2.51	1209	6	0.01	77	810	<2	85	<20	68	<0.01	<10	32	<10	16	56
11	143511	2.0	0.26	>10000	45	<5	5.76	16	32	37	31	5.50	<10	2.35	1925	3	0.01	68	530	<2	495	<20	54	<0.01	<10	19	<10	10	54
12	143512	<0.2	0.57	170	80	10	5.88	1	44	77	50	6.27	10	2.31	1093	5	0.03	86	910	4	55	<20	61	<0.01	<10	151	<10	21	67
13	143513	<0.2	0.60	60	70	10	6.29	<1	45	91	51	7.04	10	3.38	1282	6	0.02	97	1040	4	55	<20	61	<0.01	<10	169	<10	23	75
14	143514	<0.2	0.63	125	60	15	5.59	1	45	91	49	8.31	<10	2.92	972	7	0.02	101	1070	4	145	<20	44	<0.01	<10	164	<10	12	71
15	143515	<0.2	0.48	90	60	5	8.52	<1	38	76	42	5.71	<10	3.64	1119	5	0.02	77	790	4	60	<20	66	<0.01	<10	140	<10	16	64
16	143516	2.0	0.25	>10000	40	10	5.03	80	30	41	32	4.94	<10	2.09	1204	6	0.02	67	330	<2	205	<20	60	<0.01	<10	20	<10	5	52
17	143517	2.2	0.25	>10000	40	10	5.77	96	30	39	34	5.34	<10	2.43	1321	7	0.01	66	390	2	290	<20	50	<0.01	<10	28	<10	6	47
18	143518	0.6	0.37	9090	55	<5	5.89	31	37	41	41	5.87	<10	2.50	1309	4	0.01	81	900	<2	120	<20	55	<0.01	<10	34	<10	13	69
19	143519	<0.2	0.50	55	75	10	4.93	<1	48	73	47	6.56	<10	2.74	1088	6	0.03	92	940	4	45	<20	44	<0.01	<10	114	<10	18	81
20	143520	<0.2	0.51	100	60	<5	5.33	<1	41	122	52	6.33	<10	2.78	1030	4	0.03	139	1130	4	55	<20	42	<0.01	<10	113	<10	16	74
21	143521	<0.2	0.55	<5	220	10	4.41	<1	43	85	47	6.39	10	2.66	1066	4	0.04	98	1600	6	30	<20	45	<0.01	<10	129	<10	20	76
22	143522	<0.2	1.31	<5	455	10	6.79	<1	29	85	34	5.61	10	2.38	875	<1	0.06	73	1510	22	<5	<20	99	0.08	<10	98	<10	24	70
23	143523	<0.2	1.03	<5	320	10	5.05	<1	40	90	46	7.02	10	2.59	1119	4	0.07	103	1720	16	10	<20	71	<0.01	<10	124	<10	22	86
24	143524	<0.2	0.50	<5	105	10	4.39	<1	36	88	44	5.86	<10	2.46	907	5	0.04	74	1520	6	25	<20	46	<0.01	<10	143	<10	25	96
25	143525	<0.2	1.15	<5	160	5	3.88	<1	35	85	40	6.39	10	2.32	951	5	0.07	74	1800	18	5	<20	54	<0.01	<10	141	<10	25	87
26	143526	<0.2	1.74	<5	240	10	5.92	<1	36	100	43	6.01	20	2.54	989	2	0.09	78	1740	28	<5	<20	90	0.06	<10	118	<10	27	80
27	143527	<0.2	0.79	5	200	<5	6.03	<1	39	91	45	6.52	10	2.54	1150	5	0.06	91	1440	10	<5	<20	75	<0.01	<10	119	<10	21	77
28	143528	<0.2	1.07	<5	245	15	4.55	<1	43	92	46	6.49	10	1.93	1122	4	0.06	93	1400	12	20	<20	53	0.02	<10	130	<10	27	82
29	143529	0.2	0.55	1295	45	5	4.27	3	47	67	56	7.81	<10	2.07	1168	7	0.03	105	1090	2	165	<20	51	<0.01	<10	75	<10	14	83
30	143530	<0.2	0.50	20	85	10	6.78	<1	37	78	41	5.94	<10	3.19	1145	4	0.03	78	660	6	45	<20	64	<0.01	<10	112	<10	15	64

Et #.	Tag #	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
31	143531	<0.2	0.47	<5	180	5	5.21	<1	39	80	46	6.51	<10	2.79	1167	9	0.04	80	780	4	35	<20	44	<0.01	<10	138	<10	18	71
32	143532	<0.2	0.42	1045	65	10	6.78	1	40	54	38	6.71	<10	3.02	1309	6	0.04	83	450	4	75	<20	51	<0.01	<10	87	<10	9	67
33	143533	0.7	0.43	3090	55	<5	5.52	<1	45	34	46	6.36	<10	2.51	1213	6	0.04	99	620	4	90	<20	62	<0.01	<10	57	<10	11	73
34	143534	1.8	0.28	>10000	60	10	5.78	6	36	47	38	6.47	<10	2.70	1654	6	0.04	73	480	8	175	<20	57	<0.01	<10	24	<10	10	63
35	143535	2.7	0.29	>10000	50	10	4.55	27	38	27	46	6.59	<10	2.06	1566	5	0.05	76	530	<2	345	<20	46	<0.01	<10	23	<10	8	68
36	143536	<0.2	0.35	1235	50	10	3.70	<1	45	20	53	6.87	<10	1.85	1189	6	0.09	83	680	<2	120	<20	49	<0.01	<10	30	<10	9	79
37	143537	0.7	0.45	3870	70	15	5.46	25	43	67	51	6.79	<10	2.67	1423	6	0.07	93	660	6	155	<20	50	<0.01	<10	102	<10	16	76
38	143538	<0.2	0.43	265	90	<5	5.48	2	41	69	49	6.11	<10	2.77	1106	5	0.07	79	620	2	75	<20	47	<0.01	<10	94	<10	16	77
39	143539	0.4	0.33	2895	55	10	4.62	16	44	36	50	6.88	<10	2.22	1364	6	0.06	89	460	4	260	<20	59	<0.01	<10	46	<10	9	91
40	143540	<0.2	1.11	20	225	5	6.23	<1	34	82	40	5.59	<10	2.25	940	1	0.09	67	710	20	35	<20	67	0.08	<10	120	<10	20	66
41	143541	<0.2	3.08	10	405	10	5.71	<1	43	109	54	7.05	<10	3.95	1197	<1	0.17	85	900	46	5	<20	160	0.21	<10	135	<10	33	78
42	143542	<0.2	1.91	5	325	10	7.37	<1	34	94	37	5.22	<10	2.48	939	<1	0.09	60	710	32	<5	<20	157	0.15	<10	110	<10	24	58
43	143543	<0.2	2.67	5	165	10	7.51	<1	41	115	53	6.72	<10	3.33	1162	<1	0.12	81	900	38	<5	<20	143	0.12	<10	154	<10	28	76
44	143544	<0.2	0.44	5	110	10	6.49	<1	34	62	40	5.54	<10	2.38	898	4	0.07	64	780	4	25	<20	92	<0.01	<10	99	<10	16	87
45	143545	<0.2	0.43	5	165	<5	6.85	<1	32	62	41	5.66	<10	2.51	944	4	0.08	62	790	6	15	<20	99	<0.01	<10	82	<10	16	103
46	143546	<0.2	0.49	<5	360	5	4.27	<1	39	69	57	6.49	<10	2.85	979	5	0.08	75	850	6	20	<20	60	<0.01	<10	111	<10	14	72
47	143547	<0.2	0.35	90	90	<5	7.73	<1	37	80	44	5.25	<10	3.58	1018	4	0.04	96	380	<2	35	<20	94	<0.01	<10	99	<10	3	53
48	143548	<0.2	0.30	115	45	5	>10	<1	24	109	25	4.67	<10	6.42	1140	2	0.04	85	160	<2	35	<20	172	<0.01	<10	99	<10	<1	42
49	143549	<0.2	0.31	185	55	5	>10	2	33	117	42	4.91	<10	5.16	1383	3	0.04	130	440	<2	50	<20	166	<0.01	<10	96	<10	4	52
50	143550	0.2	0.32	2940	65	5	9.34	14	39	97	33	4.87	<10	3.84	1578	4	0.05	183	540	4	55	<20	174	<0.01	<10	77	<10	4	54
51	143551	0.2	0.36	2525	55	10	6.82	11	44	83	49	6.17	<10	3.22	1008	4	0.05	165	40	4	60	<20	100	<0.01	<10	72	<10	5	61
52	143552	<0.2	0.45	80	90	<5	6.22	<1	42	126	59	6.33	<10	3.86	1004	4	0.05	134	30	<2	45	<20	57	<0.01	<10	155	<10	4	74
53	143553	<0.2	0.46	5	260	<5	5.59	<1	42	132	59	6.77	<10	3.36	1087	4	0.08	133	500	2	15	<20	66	<0.01	<10	170	<10	15	73
54	143554	<0.2	0.54	5	190	10	5.57	<1	39	135	56	6.28	<10	3.23	1042	4	0.09	112	550	6	15	<20	70	<0.01	<10	158	<10	18	70
55	143555	<0.2	0.48	25	60	10	5.58	<1	43	170	55	6.44	<10	3.10	967	4	0.04	145	60	8	25	<20	47	<0.01	<10	191	<10	10	79
56	143556	<0.2	0.45	690	55	10	6.77	3	40	148	53	6.30	<10	3.50	1062	5	0.06	125	270	4	30	<20	49	<0.01	<10	169	<10	12	70
57	143557	<0.2	0.49	15	110	10	4.59	<1	53	151	63	7.05	<10	2.87	1023	4	0.08	180	580	6	20	<20	59	<0.01	<10	173	<10	18	79
58	143558	<0.2	0.45	80	80	<5	6.40	<1	47	146	58	7.17	<10	3.53	1114	5	0.06	141	400	2	30	<20	57	<0.01	<10	161	<10	12	72
59	143559	<0.2	0.49	20	115	<5	5.89	<1	37	156	63	6.38	<10	2.93	1034	4	0.06	133	550	4	35	<20	66	<0.01	<10	184	<10	19	75
60	143560	<0.2	0.43	70	85	15	5.95	<1	47	150	58	6.73	<10	2.89	1073	5	0.06	177	430	6	40	<20	56	<0.01	<10	159	<10	15	72
61	143561	<0.2	0.47	150	55	10	6.41	<1	43	157	59	6.27	<10	3.02	1041	4	0.06	153	520	2	40	<20	49	<0.01	<10	160	<10	15	73
62	143562	0.4	0.26	>10000	50	5	7.70	33	37	80	40	6.16	<10	3.36	1505	3	0.04	147	470	<2	95	<20	89	<0.01	<10	36	<10	9	64
63	143563	1.2	0.25	>10000	40	10	7.97	99	33	44	28	5.03	<10	3.49	1308	4	0.04	110	60	2	130	<20	107	<0.01	<10	30	<10	4	38
64	143564	0.3	0.31	5365	55	<5	4.87	13	46	45	54	7.02	<10	2.51	1251	6	0.05	127	470	<2	75	<20	66	<0.01	<10	30	<10	11	84
65	143565	<0.2	0.45	90	100	10	4.27	<1	43	99	52	6.59	<10	2.32	983	5	0.08	116	660	8	25	<20	65	<0.01	<10	119	<10	20	80
66	143566	<0.2	0.80	230	115	5	5.99	2	41	117	53	6.15	<10	2.38	1114	3	0.11	113	710	8	5	<20	90	0.02	<10	126	<10	20	66
67	143567	<0.2	0.96	30	160	10	4.20	<1	43	112	56	6.34	<10	2.35	955	<1	0.12	117	690	8	<5	<20	67	0.05	<10	154	<10	18	71
68	143568	<0.2	0.89	<5	145	15	5.64	<1	39	95	52	6.05	<10	2.10	986	4	0.12	100	700	12	10	<20	99	0.03	<10	126	<10	22	63
69	143569	<0.2	0.49	10	65	<5	5.72	<1	42	111	56	6.23	<10	2.74	1095	4	0.08	97	730	<2	20	<20	44	<0.01	<10	188	<10	20	65
70	143570	<0.2	0.43	60	110	10	5.71	<1	41	89	54	6.18	<10	3.00	1111	5	0.07	89	590	4	25	<20	73	<0.01	<10	109	<10	19	72

E	Ta	A	%	Ba	Ca	d	Cr	Fe %	Mg	In	I	Na %	P	Sb	S	%	V	Y											
71	143571	<0.2	0.72	10	205	<5	6.15	<1	39	105	53	6.48	<10	2.85	1137	4	0.11	96	680	6	20	<20	66	0.02	<10	159	<10	21	69
72	143572	<0.2	2.11	5	80	10	6.87	<1	39	124	50	5.64	<10	2.74	967	<1	0.13	85	720	30	10	<20	132	0.14	<10	122	<10	21	62
73	143573	<0.2	1.03	<5	245	10	5.59	<1	37	97	49	5.90	<10	2.85	1057	2	0.14	85	700	10	<5	<20	121	0.02	<10	125	<10	20	64
74	143574	<0.2	1.57	<5	300	10	4.82	1	41	123	57	6.77	<10	3.32	1146	3	0.14	95	730	18	5	<20	122	0.04	<10	148	<10	20	68
75	143575	<0.2	1.05	<5	240	5	7.27	<1	34	92	45	5.69	10	2.43	937	4	0.11	74	720	6	<5	<20	140	<0.01	<10	114	<10	17	61
76	143576	<0.2	1.37	10	120	15	8.45	<1	40	133	52	6.82	<10	2.89	1340	4	0.12	108	730	18	<5	<20	236	<0.01	<10	136	<10	19	70
77	143577	<0.2	1.53	10	205	<5	6.93	<1	43	167	61	5.93	<10	2.85	997	2	0.18	142	620	18	<5	<20	187	0.01	<10	148	<10	21	62
78	143578	<0.2	0.89	<5	125	15	6.64	2	40	93	47	6.99	<10	3.01	1260	5	0.15	76	700	6	5	<20	86	<0.01	<10	199	<10	18	70

**C DATA:**

**Repeat:**

1	143501	<0.2	4.02	5	80	10	5.69	<1	46	180	52	7.74	30	4.46	1512	5	0.07	141	1680	40	<5	<20	111	0.01	<10	148	<10	24	84
10	143510	<0.2	0.38	460	60	10	5.26	2	42	33	40	6.22	<10	2.31	1196	6	0.01	78	870	<2	85	<20	60	<0.01	<10	30	<10	16	64
19	143519	<0.2	0.48	55	70	10	4.93	<1	49	74	48	6.58	<10	2.77	1093	7	0.02	92	950	6	45	<20	45	<0.01	<10	114	<10	18	81
36	143536	<0.2	0.34	1300	50	15	4.00	5	48	21	56	7.25	<10	1.95	1249	6	0.10	91	730	4	125	<20	55	<0.01	<10	31	<10	12	83
45	143545	<0.2	0.41	5	155	5	6.93	<1	34	62	43	5.73	<10	2.57	958	4	0.08	61	780	4	10	<20	99	<0.01	<10	83	<10	15	108
54	143554	<0.2	0.47	10	165	10	5.31	<1	37	125	50	5.97	<10	3.08	989	4	0.09	111	540	6	20	<20	60	<0.01	<10	149	<10	16	67
71	143571	<0.2	0.80	10	235	<5	6.31	<1	39	109	57	6.62	<10	3.04	1172	3	0.11	96	670	4	10	<20	74	0.02	<10	167	<10	22	77

**esplits:**

1	143501	<0.2	3.67	10	75	10	5.63	<1	45	176	48	7.61	20	4.04	1466	4	0.06	142	1710	42	<5	<20	101	0.01	<10	140	<10	21	90
36	143536	<0.2	0.33	1270	55	15	4.02	4	47	19	56	7.01	<10	1.91	1213	6	0.10	86	670	2	110	<20	56	<0.01	<10	30	<10	11	81
71	143571	<0.2	0.74	5	205	5	6.40	<1	39	111	58	6.72	<10	3.08	1193	4	0.12	96	680	4	<5	<20	67	0.02	<10	170	<10	23	71

**Standard:**

7b106	>30	0.55	270	85	<5	1.63	32	3	40	6293	1.61	<10	0.19	570	31	0.02	7	270	5272	55	<20	139	<0.01	<10	13	<10	1	8301
7b106	>30	0.53	270	80	<5	1.64	31	4	41	6188	1.66	<10	0.18	564	29	0.02	7	270	5282	60	<20	135	<0.01	<10	13	<10	1	8465
7b106	>30	0.54	275	80	<5	1.69	32	3	40	6226	1.60	<10	0.18	575	33	0.02	7	280	5316	55	<20	132	<0.01	<10	13	<10	1	8464

**ECO TECH LABORATORY LTD.**

Jutta Jealouse

B.C. Certified Assayer

JJ/bp  
Jf/1845  
XLS/06



# CERTIFICATE OF ASSAY AK 2006-2033

LEVON RESOURCES LTD.  
Suite 400-455 Granville Street  
Vancouver, BC  
V6C 1T1

5-Dec-06

No. of samples received: 43  
Sample Type: Core  
Project #: GL06- 2 & 3  
Samples submitted by : C. Kauss

ET #.	Tag #	Au (g/t)	Au (oz/t)
1	143579	1.08	0.031
2	143580	0.60	0.017
3	143581	<0.03	<0.001
4	143582	<0.03	<0.001
5	143583	<0.03	<0.001
6	143584	<0.03	<0.001
7	143585	0.07	0.002
8	143586	<0.03	<0.001
9	143587	<0.03	<0.001
10	143588	<0.03	<0.001
11	143589	0.03	0.001
12	143590	<0.03	<0.001
13	143591	<0.03	<0.001
14	143592	<0.03	<0.001
15	143593	4.56	0.133
16	143594	6.75	0.197
17	143595	<0.03	<0.001
18	143596	<0.03	<0.001
19	143597	<0.03	<0.001
20	143598	0.03	0.001
21	143599	<0.03	<0.001
22	143600	0.20	0.006
23	143601	<0.03	<0.001
24	143602	<0.03	<0.001
25	143603	<0.03	<0.001
26	143604	<0.03	<0.001
27	143605	<0.03	<0.001
28	143606	<0.03	<0.001
29	143607	<0.03	<0.001
30	143608	0.87	0.025
31	143609	<0.03	<0.001

GL-06-02

GL-06-03

**ECO TECH LABORATORY LTD.**  
Jutta Jealouse  
B.C. Certified Assayer

ET #.	Tag #	Au (g/t)	Au (oz/t)
32	143610	<0.03	<0.001
33	143611	<0.03	<0.001
34	143612	<0.03	<0.001
35	143613	0.11	0.003
36	143614	<0.03	<0.001
37	143615	<0.03	<0.001
38	143616	<0.03	<0.001
39	143617	0.04	0.001
40	143618	5.48	0.160
41	143619	0.20	0.006
42	143620	<0.03	<0.001
43	143621	<0.03	<0.001

GL-06-03

QC DATA:

**Repeat:**

1	143579	1.05	0.031
2	143580	0.63	0.018
10	143588	<0.03	<0.001
15	143593	4.74	0.138
16	143594	7.13	0.208
19	143597	<0.03	<0.001
30	143608	0.91	0.027
36	143614	<0.03	<0.001
40	143618	5.42	0.158

**Resplit:**

36	143614	<0.03	<0.001
----	--------	-------	--------

**Standard:**

SI25	1.79	0.052
SI25	1.83	0.053

JJ/kc  
XLS/06

**ECO TECH LABORATORY LTD.**

Jutta Jealouse  
B.C. Certified Assayer

ECO TECH LABORATORY LTD.  
 041 Dallas Drive  
 NANAIMO, B.C.  
 V9C 6T4

## ICP CERTIFICATE OF ANALYSIS AK 2006-2033

LEVON RESOURCES LTD.  
 Suite 400-455 Granville Street  
 Vancouver, BC  
 V6C 1T1

Phone: 250-573-5700

Fax: 250-573-4557

No. of samples received: 43

Sample Type: Core

Project #: GL06- 2 &amp; 3

Samples submitted by: C. Kauss

Values in ppm unless otherwise reported

Et #.	Tag #	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Tl %	U	V	W	Y	Zn
1	143579	1.2	0.56	7110	65	15	4.08	<1	34	50	54	6.27	<10	2.80	1180	5	0.01	70	680	8	1245	<20	53	<0.01	<10	56	<10	17	72
2	143580	0.5	0.70	5195	60	15	4.26	<1	37	60	50	6.07	<10	2.47	1152	6	0.02	75	730	8	840	<20	69	<0.01	<10	69	<10	18	68
3	143581	<0.2	0.83	15	185	10	6.49	<1	30	69	38	5.68	20	3.44	1036	5	0.05	79	1270	14	15	<20	59	<0.01	<10	126	<10	20	70
4	143582	<0.2	0.80	10	130	10	6.11	1	30	81	36	5.36	10	2.79	904	7	0.05	76	1450	12	30	<20	52	<0.01	<10	141	<10	22	74
5	143583	<0.2	0.59	<5	85	15	5.50	1	39	99	51	6.17	10	2.66	1056	6	0.03	103	1590	4	30	<20	47	<0.01	<10	135	<10	23	82
6	143584	<0.2	0.57	20	60	15	8.37	<1	30	65	44	6.10	10	4.51	1196	5	0.02	47	1320	6	45	<20	69	<0.01	<10	142	<10	20	69
7	143585	<0.2	0.75	705	135	10	6.88	<1	27	72	37	5.35	10	3.07	1142	5	0.04	69	1200	8	90	<20	74	<0.01	<10	107	<10	19	62
8	143586	<0.2	0.80	20	160	15	6.93	<1	34	88	42	6.02	10	3.55	1095	5	0.08	97	1240	14	25	<20	97	<0.01	<10	112	<10	22	68
9	143587	<0.2	1.19	10	305	10	5.98	<1	34	86	44	6.14	20	3.89	1105	5	0.09	100	1290	16	25	<20	75	<0.01	<10	123	<10	19	76
10	143588	<0.2	1.03	10	150	10	4.52	<1	39	83	41	6.10	10	3.07	1051	5	0.14	111	1260	16	10	<20	53	<0.01	<10	127	<10	17	71
11	143589	<0.2	0.80	<5	170	15	5.46	<1	39	135	44	6.52	<10	3.42	1120	6	0.07	120	1020	12	40	<20	132	<0.01	<10	157	<10	18	79
12	143590	<0.2	0.66	40	125	10	5.05	<1	34	92	42	6.22	<10	3.18	1104	5	0.05	95	1120	12	60	<20	127	<0.01	<10	111	<10	14	75
13	143591	<0.2	0.68	35	155	5	5.74	<1	32	95	42	5.67	<10	3.43	1003	5	0.05	96	1120	10	65	<20	153	<0.01	<10	110	<10	13	72
14	143592	<0.2	0.51	285	95	10	5.58	<1	33	77	41	5.56	<10	3.06	1176	5	0.05	101	1030	8	90	<20	93	<0.01	<10	74	<10	15	75
15	143593	2.6	0.29	>10000	45	10	5.04	<1	25	57	32	4.93	<10	2.58	1760	6	0.05	81	770	4	7430	<20	83	<0.01	<10	27	<10	8	58
16	143594	1.4	0.37	>10000	60	15	4.23	<1	26	92	25	5.42	<10	2.16	1328	5	0.05	75	800	8	185	<20	62	<0.01	<10	25	<10	9	62
17	143595	<0.2	2.93	30	170	20	6.14	<1	36	132	43	6.17	20	3.16	1056	<1	0.13	104	1380	38	20	<20	114	0.16	<10	149	<10	27	76
18	143596	<0.2	2.08	20	130	10	4.24	<1	42	101	52	6.47	10	1.54	1140	7	0.11	100	1580	32	10	<20	74	0.01	<10	88	<10	26	148
19	143597	<0.2	1.73	10	70	10	2.97	<1	38	74	70	6.16	10	1.08	838	6	0.09	89	1470	28	<5	<20	51	0.01	<10	47	<10	28	131
20	143598	<0.2	1.54	100	70	15	2.52	<1	41	83	63	6.44	10	1.56	1036	5	0.09	114	1660	30	20	<20	48	0.05	<10	62	<10	33	147
21	143599	<0.2	2.51	35	65	<5	3.13	<1	39	135	133	6.36	10	3.11	1184	8	0.09	143	1260	46	20	<20	49	<0.01	<10	105	<10	17	109
22	143600	0.3	0.40	1165	50	10	2.44	<1	16	82	47	3.99	<10	1.27	668	11	0.07	65	650	14	45	<20	29	<0.01	<10	27	<10	9	96
23	143601	<0.2	0.67	120	135	5	3.91	<1	45	67	62	6.51	<10	2.47	1234	5	0.04	102	900	12	55	<20	34	<0.01	<10	97	<10	15	106
24	143602	<0.2	0.54	970	75	15	5.69	<1	37	60	53	6.77	<10	3.44	1378	6	0.03	81	780	10	100	<20	56	<0.01	<10	91	<10	20	81
25	143603	0.2	0.51	305	85	15	7.97	<1	31	58	39	5.90	<10	2.85	1258	5	0.03	63	650	8	80	<20	101	<0.01	<10	77	<10	17	63
26	143604	<0.2	0.60	10	115	15	6.90	<1	31	77	35	5.26	<10	3.35	916	6	0.05	65	630	12	25	<20	52	<0.01	<10	138	<10	19	62
27	143605	0.3	1.38	15	95	15	5.67	<1	38	79	44	6.17	<10	3.14	1051	2	0.06	82	720	24	10	<20	68	0.05	<10	124	<10	22	75
28	143606	<0.2	0.48	10	95	10	7.41	<1	35	53	37	5.27	<10	3.59	1122	5	0.10	61	680	12	15	<20	39	<0.01	<10	139	<10	17	56
29	143607	<0.2	0.70	175	90	10	5.84	<1	35	80	38	5.18	<10	2.52	1071	5	0.05	79	680	12	35	<20	39	<0.01	<10	123	<10	17	65
30	143608	0.7	0.47	9425	65	5	5.66	<1	35	48	41	5.74	<10	3.02	1407	6	0.02	81	570	10	255	<20	57	<0.01	<10	59	<10	12	80

Et #.	Tag #	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
31	143609	<0.2	0.61	45	60	15	4.70	<1	43	76	46	6.12	<10	2.33	1253	6	0.03	93	840	128	50	<20	27	<0.01	<10	172	<10	17	80
32	143610	<0.2	0.60	145	120	15	6.24	<1	40	117	48	5.84	<10	2.90	1230	6	0.04	110	720	10	50	<20	29	<0.01	<10	131	<10	13	71
33	143611	<0.2	0.47	20	65	15	7.68	<1	32	86	34	6.49	<10	4.00	1028	5	0.03	97	1220	8	55	<20	61	<0.01	<10	142	<10	18	77
34	143612	<0.2	0.64	15	70	15	7.60	<1	32	89	35	5.86	<10	4.03	925	5	0.04	92	1060	10	55	<20	63	<0.01	<10	141	<10	20	72
35	143613	<0.2	0.53	1625	100	5	7.65	<1	29	77	33	5.44	<10	4.01	998	4	0.05	77	950	8	90	<20	72	<0.01	<10	81	<10	13	63
36	143614	<0.2	0.65	45	140	15	3.98	<1	34	70	43	6.50	10	2.53	1114	6	0.07	82	1440	16	50	<20	54	<0.01	<10	97	<10	24	91
37	143615	<0.2	0.85	50	275	10	6.04	<1	28	97	34	5.60	10	2.82	989	5	0.09	72	1290	14	25	<20	61	<0.01	<10	104	<10	19	70
38	143616	<0.2	0.59	110	95	20	5.04	<1	36	84	41	6.14	10	2.78	964	5	0.08	99	1530	12	50	<20	51	<0.01	<10	88	<10	23	79
39	143617	<0.2	0.67	215	100	10	4.67	<1	34	92	37	5.54	<10	2.48	897	5	0.08	100	1640	14	50	<20	44	<0.01	<10	98	<10	24	69
40	143618	3.2	0.33	>10000	60	10	3.55	<1	29	53	29	5.18	<10	2.01	1404	5	0.05	70	630	14	4635	<20	57	<0.01	<10	26	<10	10	71
41	143619	0.2	0.94	3305	100	5	6.31	<1	36	86	40	5.61	10	2.47	1202	4	0.08	106	1530	16	85	<20	95	<0.01	<10	81	<10	20	78
42	143620	<0.2	2.16	25	410	10	7.79	<1	28	95	36	5.24	20	2.34	1042	4	0.10	65	1450	38	15	<20	142	0.01	<10	115	<10	18	73
43	143621	<0.2	3.07	20	105	15	4.93	<1	56	104	92	7.14	<10	1.45	1413	<1	0.14	110	930	54	5	<20	94	0.19	<10	102	<10	40	175

**C DATA:**

**Repeat:**

1	143579	1.1	0.54	7165	60	5	4.06	<1	35	50	53	6.34	<10	2.80	1192	6	0.01	73	730	8	1270	<20	49	<0.01	<10	56	<10	16	74
10	143588	<0.2	1.02	5	160	15	4.58	<1	37	84	43	6.17	10	3.13	1067	6	0.14	108	1260	16	15	<20	56	<0.01	<10	128	<10	17	73
19	143597	<0.2	1.62	15	70	15	2.94	<1	38	71	65	6.10	10	1.01	820	6	0.08	89	1520	34	<5	<20	50	0.01	<10	45	<10	27	106

**Resplit:**

1	143579	0.9	0.49	7055	60	15	4.18	<1	36	44	55	6.50	<10	2.68	1219	7	0.01	75	740	12	1360	<20	49	<0.01	<10	58	<10	18	86
36	143614	<0.2	0.71	45	140	15	3.95	<1	36	71	40	5.97	<10	2.34	972	6	0.08	91	1490	18	45	<20	57	<0.01	<10	100	<10	26	85

**Standard:**

B106	>30	0.54	275	70	<5	1.75	45	3	44	6284	1.33	<10	0.23	539	30	0.02	6	270	5232	45	<20	144	<0.01	<10	14	10	<1	8382
B106	>30	0.51	275	75	<5	1.79	46	4	40	6237	1.35	<10	0.25	289	28	0.02	7	280	5270	55	<20	146	<0.01	<10	15	10	<1	8391

**ECO TECH LABORATORY LTD.**

Jutta Jealous

B.C. Certified Assayer

JJ/sa  
11/2055  
XLS/06

# CERTIFICATE OF ASSAY AK 2006-2106

LEVON RESOURCES LTD.  
Suite 400-455 Granville Street  
Vancouver, BC  
V6C 1T1

12-Dec-06

LEVON

No. of samples received: 64  
Sample Type: Core  
Project #: LZ  
Samples submitted by: C. Kauss

ET #.	Tag #	Au (g/t)	Au (oz/t)	
1	143622	<0.03	<0.001	
2	143623	<0.03	<0.001	
3	143624	<0.03	<0.001	
4	143625	<0.03	<0.001	
5	143626	<0.03	<0.001	
6	143627	<0.03	<0.001	
7	143628	<0.03	<0.001	
8	143629	<0.03	<0.001	
9	143630	<0.03	<0.001	GL-06-04
10	143631	<0.03	<0.001	
11	143632	<0.03	<0.001	
12	143633	<0.03	<0.001	
13	143634	3.38	0.099	
14	143635	0.04	0.001	
15	143636	<0.03	<0.001	
16	143637	<0.03	<0.001	
17	143638	3.80	0.111	
18	143639	2.38	0.069	
19	143640	0.03	0.001	GL-06-05
20	143641	<0.03	<0.001	
21	143642	<0.03	<0.001	
22	143643	<0.03	<0.001	
23	143647	<0.03	<0.001	
24	143648	0.03	0.001	
25	143649	0.13	0.004	
26	143650	<0.03	<0.001	

ECO TECH LABORATORY LTD.  
Jutta Jealous  
B.C. Certified Assayer

ET #.	Tag #	Au (g/t)	Au (oz/t)
27	143651	<0.03	<0.001
28	143652	<0.03	<0.001
29	143653	0.04	0.001
30	143654	<0.03	<0.001
31	143655	<0.03	<0.001
32	143656	0.07	0.002
33	143657	0.06	0.002
34	143658	<0.03	<0.001
35	143659	0.20	0.006
36	143660	<0.03	<0.001
37	143661	<0.03	<0.001
38	143662	<0.03	<0.001
39	143663	<0.03	<0.001
40	143664	<0.03	<0.001
41	143665	0.05	0.001
42	143666	0.38	0.011
43	143667	0.05	0.001
44	143668	<0.03	<0.001
45	143669	0.34	0.010
46	143670	0.06	0.002
47	143671	0.09	0.003
48	143672	<0.03	<0.001
49	143673	<0.03	<0.001
50	143674	<0.03	<0.001
51	143675	0.07	0.002
52	143676	0.16	0.005
53	143677	0.04	0.001
54	143678	1.92	0.056
55	143679	0.16	0.005
56	143680	2.19	0.064
57	143681	0.33	0.010
58	143682	<0.03	<0.001
59	143683	<0.03	<0.001
60	143684	<0.03	<0.001
61	143685	<0.03	<0.001
62	143686	<0.03	<0.001
63	143687	0.04	0.001
64	143688	<0.03	<0.001

LZ-06-01

**QC DATA:****Repeat:**

1	143622	<0.03	<0.001
10	143631	<0.03	<0.001
13	143634	3.19	0.093
14	143635	0.05	0.001

**ECO TECH LABORATORY LTD.**

Jutta Jealouse

B.C. Certified Assayer

ET #.	Tag #	Au (g/t)	Au (oz/t)
<b>Repeat:</b>			
17	143638	3.82	0.111
18	143639	2.51	0.073
19	143640	<0.03	<0.001
25	143649	0.16	0.005
36	143660	<0.03	<0.001
45	143669	0.32	0.009
42	143666	0.45	0.013
54	143678	1.90	0.055
56	143680	2.34	0.068
<b>Resplit:</b>			
1	143622	<0.03	<0.001
36	143660	<0.03	<0.001
<b>Standard:</b>			
SJ10		2.59	0.076
SJ10		2.63	0.077

JJ/sa  
XLS/06

**ECO TECH LABORATORY LTD.**  
Jutta Jealouse  
B.C. Certified Assayer

ECO TECH LABORATORY LTD.  
1041 Dallas Drive  
AMLOOPS, B.C.  
V6C 6T4

## ICP CERTIFICATE OF ANALYSIS AK 2006-2106

LEVON RESOURCES LTD.  
Suite 400-455 Granville Street  
Vancouver, BC  
V6C 1T1

Phone: 250-573-5700  
Fax: 250-573-4557

No. of samples received: 64  
Sample Type: Core  
Project #: LZ  
Samples submitted by: C. Kauss

Values in ppm unless otherwise reported

Et #.	Tag #	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Tl %	U	V	W	Y	Zn
1	143622	<0.2	3.56	5	310	15	6.97	1	44	114	54	7.07	10	3.94	1546	4	0.08	88	880	40	15	<20	133	0.12	<10	154	<10	29	71
2	143623	<0.2	5.01	<5	65	15	5.31	2	53	157	71	7.64	20	4.95	1491	<1	0.08	96	930	50	45	<20	67	0.37	<10	240	<10	38	70
3	143624	<0.2	0.53	<5	90	5	7.56	<1	36	114	52	5.73	<10	2.96	1117	7	0.05	86	740	4	15	<20	92	0.01	<10	137	<10	15	52
4	143625	<0.2	0.57	<5	60	5	5.98	<1	42	119	57	5.78	<10	2.57	1075	5	0.03	93	710	4	10	<20	44	<0.01	<10	192	<10	18	55
5	143626	<0.2	0.43	<5	60	10	>10	<1	31	65	42	6.51	<10	5.66	1190	6	0.03	67	310	<2	30	<20	61	<0.01	<10	126	<10	9	56
6	143627	<0.2	0.43	<5	115	10	7.91	1	38	56	51	6.74	<10	4.38	1452	5	0.04	75	430	4	15	<20	68	<0.01	<10	140	<10	14	61
7	143628	<0.2	0.95	<5	215	5	8.05	1	41	65	58	6.16	<10	4.06	1695	6	0.11	81	640	8	25	<20	66	0.02	<10	127	<10	19	58
8	143629	<0.2	0.64	<5	155	10	7.16	<1	30	70	47	5.17	<10	3.64	1309	4	0.09	62	610	4	10	<20	71	<0.01	<10	124	<10	19	52
9	143630	<0.2	0.99	<5	320	15	4.84	<1	38	92	62	6.79	10	2.85	1092	3	0.14	79	870	10	<5	<20	92	0.01	<10	146	<10	24	68
10	143631	<0.2	2.05	<5	555	15	6.82	<1	36	95	51	6.23	<10	3.47	1079	6	0.13	72	780	24	20	<20	142	0.05	<10	127	<10	24	62
11	143632	<0.2	1.19	<5	270	10	5.55	2	39	85	54	6.82	<10	3.53	1076	10	0.13	78	790	14	45	<20	64	0.02	<10	139	<10	25	67
12	143633	<0.2	1.06	10	270	10	5.02	1	37	78	53	6.27	<10	3.00	1053	7	0.12	70	820	10	30	<20	69	<0.01	<10	127	<10	24	62
13	143634	0.7	0.35	4490	75	<5	7.88	6	30	56	35	5.07	<10	3.53	1564	5	0.04	95	290	<2	85	<20	146	<0.01	<10	61	<10	3	49
14	143635	<0.2	0.57	385	95	10	7.03	2	42	123	24	5.68	<10	4.15	1223	5	0.06	185	900	<2	70	<20	141	<0.01	<10	129	<10	4	48
15	143636	<0.2	0.45	<5	195	10	>10	1	32	58	44	4.89	<10	4.86	1059	3	0.07	50	500	<2	25	<20	71	0.01	<10	112	<10	11	56
16	143637	<0.2	1.00	<5	545	5	6.82	<1	30	74	35	5.25	<10	2.72	1092	4	0.10	51	610	12	30	<20	64	0.02	<10	131	<10	17	52
17	143638	0.9	0.24	8795	55	<5	3.67	20	21	40	69	4.31	<10	1.61	1071	9	0.05	93	980	6	115	<20	55	<0.01	<10	12	<10	15	77
18	143639	2.1	0.38	>10000	65	10	5.36	25	36	54	40	5.55	<10	2.23	1772	3	0.06	103	1170	8	135	<20	87	0.02	<10	23	<10	18	158
19	143640	<0.2	1.34	515	110	15	7.42	1	36	87	44	5.90	10	2.90	1195	5	0.10	108	1350	16	45	<20	129	<0.01	<10	89	<10	19	67
20	143641	<0.2	2.33	15	150	15	6.13	<1	35	87	40	6.17	20	3.12	1097	7	0.13	77	1670	32	10	<20	131	<0.01	<10	125	<10	26	75
21	143642	<0.2	0.71	25	110	10	4.70	<1	47	74	52	6.56	<10	2.62	1193	4	0.08	99	1470	12	10	<20	78	0.02	<10	60	<10	27	132
22	143643	<0.2	3.65	15	130	15	7.77	2	39	112	50	6.59	20	3.65	1311	11	0.09	103	1520	44	45	<20	123	0.06	<10	131	<10	27	70
23	143647	<0.2	0.92	50	195	10	3.83	1	44	102	63	7.57	10	1.17	1167	9	0.03	103	1010	12	5	<20	59	<0.01	<10	190	<10	28	74
24	143648	<0.2	0.93	165	265	10	6.62	1	42	113	64	6.42	<10	2.75	1246	7	0.02	119	490	10	30	<20	94	<0.01	<10	162	<10	20	64
25	143649	<0.2	0.72	275	120	5	7.62	1	37	78	44	5.66	10	2.13	1056	5	0.03	90	1210	10	15	<20	104	0.01	<10	91	<10	21	63
26	143650	<0.2	0.71	85	180	<5	5.27	<1	45	71	53	7.37	<10	1.95	1208	7	0.02	97	1270	8	25	<20	62	<0.01	<10	105	<10	22	95
27	143651	<0.2	0.48	95	185	15	7.85	2	43	53	51	7.69	<10	2.86	1448	9	0.02	91	910	<2	65	<20	65	<0.01	<10	77	<10	16	105
28	143652	<0.2	0.66	40	145	10	4.43	<1	37	62	55	6.95	10	2.64	1232	6	0.04	74	1650	8	35	<20	47	<0.01	<10	80	<10	36	101
29	143653	<0.2	0.56	40	150	10	3.36	<1	48	49	77	7.15	<10	2.27	1131	6	0.04	84	1120	8	40	<20	39	<0.01	<10	65	<10	25	95
30	143654	<0.2	0.70	55	150	10	3.30	1	51	86	68	6.98	<10	2.33	1185	7	0.05	99	1270	10	25	<20	33	<0.01	<10	78	<10	26	94



Et #.	Tag #	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
31	143655	<0.2	0.46	270	100	5	4.63	1	33	57	49	5.48	<10	2.32	1056	6	0.02	82	890	6	40	<20	41	<0.01	<10	50	<10	11	73
32	143656	<0.2	0.38	720	80	<5	5.00	2	25	61	44	4.58	<10	2.13	1052	6	<0.01	82	880	4	35	<20	60	<0.01	<10	26	<10	12	75
33	143657	<0.2	0.57	895	90	10	3.52	5	48	69	68	6.60	<10	2.24	1036	11	0.03	108	1170	8	75	<20	48	<0.01	<10	64	<10	18	107
34	143658	<0.2	0.28	120	65	5	2.44	<1	27	182	58	4.03	<10	2.41	1068	8	0.03	103	220	6	35	<20	15	<0.01	<10	71	<10	5	64
35	143659	0.4	0.37	1835	70	10	2.19	4	40	85	71	6.37	<10	1.83	1451	4	<0.01	191	190	8	40	<20	47	0.01	<10	48	<10	<1	94
36	143660	0.2	0.22	350	90	<5	2.65	<1	22	95	65	3.80	<10	2.95	744	8	0.01	157	30	10	45	<20	59	<0.01	<10	45	<10	2	84
37	143661	<0.2	0.58	40	185	15	2.47	<1	23	59	27	6.78	20	2.74	1272	8	0.03	39	1900	10	20	<20	61	<0.01	<10	43	<10	18	140
38	143662	<0.2	0.73	10	410	15	2.06	1	16	32	25	8.00	20	2.80	1378	15	0.02	28	960	10	15	<20	94	<0.01	<10	71	<10	9	154
39	143663	<0.2	0.62	<5	885	20	2.16	<1	17	19	14	8.38	<10	3.25	1645	11	0.01	21	900	10	15	<20	206	<0.01	<10	91	<10	7	159
40	143664	<0.2	0.47	<5	560	25	2.24	2	21	18	21	9.93	<10	3.56	1988	11	0.01	28	290	4	20	<20	131	<0.01	<10	113	<10	<1	189
41	143665	<0.2	0.38	65	140	20	3.79	1	25	34	17	7.39	20	3.52	1664	9	0.01	68	2960	8	30	<20	109	<0.01	<10	86	<10	37	134
42	143666	1.0	0.43	345	120	15	2.40	2	28	176	44	5.84	<10	3.93	1193	10	0.01	217	720	10	45	<20	109	<0.01	<10	67	<10	7	102
43	143667	<0.2	0.30	185	120	<5	2.52	2	28	176	55	3.79	<10	4.13	874	8	<0.01	274	40	6	65	<20	103	<0.01	<10	54	<10	2	65
44	143668	<0.2	0.27	275	120	<5	0.69	<1	18	110	84	2.86	<10	1.59	519	6	<0.01	149	70	6	60	<20	46	<0.01	<10	31	<10	2	83
45	143669	5.1	0.30	575	100	<5	2.43	2	36	178	55	4.18	<10	4.10	933	8	<0.01	367	50	8	65	<20	125	<0.01	<10	53	<10	1	68
46	143670	0.2	0.27	300	115	<5	3.14	2	28	187	52	4.06	<10	3.71	946	9	<0.01	313	80	4	65	<20	166	<0.01	<10	53	<10	<1	66
47	143671	0.6	0.19	145	130	<5	2.59	1	19	189	68	2.33	<10	2.04	537	6	<0.01	172	180	6	65	<20	149	<0.01	<10	26	<10	5	48
48	143672	<0.2	0.04	20	190	<5	0.48	<1	6	209	42	0.66	<10	0.25	140	7	<0.01	22	70	4	15	<20	18	<0.01	<10	4	<10	3	20
49	143673	<0.2	0.46	145	145	<5	1.50	<1	24	161	77	2.62	<10	1.75	567	4	0.04	215	140	8	60	<20	81	<0.01	<10	39	<10	1	54
50	143674	0.2	0.28	275	125	5	2.06	2	27	172	59	4.18	<10	3.21	785	9	0.01	242	150	6	75	<20	123	<0.01	<10	48	<10	2	70
51	143675	0.2	0.13	220	100	<5	1.78	<1	11	166	39	1.60	<10	1.10	453	<1	<0.01	68	100	4	30	<20	69	<0.01	<10	15	<10	2	38
52	143676	0.2	0.26	475	85	<5	2.61	1	27	169	51	3.98	<10	3.59	771	10	<0.01	323	170	6	105	<20	117	<0.01	<10	40	<10	4	59
53	143677	<0.2	0.24	215	85	<5	1.64	<1	14	89	92	2.54	<10	1.93	500	6	<0.01	91	30	10	65	<20	61	<0.01	<10	17	<10	4	74
54	143678	2.2	0.25	2345	50	<5	3.62	5	20	103	70	3.46	<10	2.48	1013	8	<0.01	176	40	8	90	<20	99	<0.01	<10	28	<10	<1	74
55	143679	0.3	0.31	700	80	<5	2.52	2	24	144	70	3.58	<10	2.55	777	8	0.01	217	100	10	70	<20	96	<0.01	<10	41	<10	<1	79
56	143680	6.9	0.27	2065	65	<5	2.93	3	28	138	65	3.96	<10	2.49	1211	8	0.01	269	40	10	80	<20	107	<0.01	<10	31	<10	2	97
57	143681	0.5	0.25	815	70	<5	2.31	2	22	86	73	3.23	<10	2.40	753	8	0.01	165	40	8	80	<20	87	<0.01	<10	22	<10	<1	90
58	143682	<0.2	0.44	40	195	<5	2.21	2	42	225	72	5.20	<10	4.37	984	10	0.02	344	80	8	55	<20	83	<0.01	<10	90	<10	<1	87
59	143683	<0.2	0.20	15	170	10	5.50	<1	11	113	24	2.08	<10	3.63	785	<1	0.01	56	80	6	20	<20	77	<0.01	<10	29	<10	6	25
60	143684	<0.2	0.46	15	265	10	2.29	1	37	207	69	4.87	<10	4.36	954	8	0.02	334	130	10	40	<20	103	<0.01	<10	91	<10	4	85
61	143685	<0.2	1.79	10	150	<5	2.77	<1	29	227	68	4.75	<10	4.77	1046	9	0.04	247	630	28	30	<20	93	<0.01	<10	94	<10	13	83
62	143686	<0.2	1.19	10	150	<5	2.84	<1	26	219	68	3.77	<10	4.23	918	9	0.03	216	450	20	30	<20	83	<0.01	<10	74	<10	10	71
63	143687	<0.2	0.99	15	155	<5	2.68	1	32	164	58	4.71	<10	4.68	887	8	0.03	238	800	22	30	<20	74	<0.01	<10	92	<10	18	92
64	143688	0.2	0.33	15	85	<5	1.24	1	15	60	70	2.84	10	1.55	452	13	0.02	68	380	18	25	<20	28	<0.01	<10	23	<10	8	103

**QC DATA:**

**Repeat:**

1	143622	<0.2	3.64	10	305	10	7.04	<1	44	114	54	7.14	20	4.06	1571	10	0.09	87	870	34	20	<20	138	0.05	<10	156	<10	28	70
10	143631	<0.2	2.10	5	565	15	7.08	1	37	98	53	6.48	<10	3.56	1118	6	0.14	76	830	26	20	<20	141	0.04	<10	130	<10	23	65
19	143640	<0.2	1.32	520	110	5	7.40	2	36	86	44	5.91	10	2.89	1194	6	0.09	108	1380	16	55	<20	126	<0.01	<10	89	<10	18	68
36	143660	0.2	0.23	360	85	<5	2.70	1	23	97	67	3.89	<10	3.04	761	9	0.01	161	30	8	55	<20	59	<0.01	<10	46	<10	2	81
45	143669	4.9	0.30	580	100	<5	2.43	3	37	175	55	4.18	<10	4.13	935	11	<0.01	376	50	10	85	<20	129	<0.01	<10	55	<10	3	67
54	143678	2.2	0.24	2490	65	<5	3.65	2	20	104	72	3.48	<10	2.48	1019	6	<0.01	174	20	10	80	<20	109	<0.01	<10	27	<10	<1	77

<u>Et #</u>	<u>Ta</u>	<u>Ar</u>	<u>As</u>	<u>Ba</u>	<u>Ca</u>	<u>Cd</u>	<u>Co</u>	<u>Cr</u>	<u>Cu</u>	<u>Fe %</u>	<u>Mg</u>	<u>Mn</u>	<u>Mo</u>	<u>Ni %</u>	<u>P</u>	<u>Pb</u>	<u>Se</u>	<u>Sn</u>	<u>Sr</u>	<u>Tl %</u>	<u>V</u>	<u>Zn</u>	<u>Zn</u>						
<b>split:</b>																													
1	143622	<0.2	3.98	15	300	10	6.72	1	48	118	56	7.23	20	4.44	1625	13	0.09	99	910	48	45	<20	141	0.04	<10	162	<10	30	77
36	143660	<0.2	0.22	310	85	5	2.69	1	22	89	60	3.89	<10	2.98	756	8	0.01	155	30	10	60	<20	59	<0.01	<10	46	<10	3	82
<b>standard:</b>																													
106		>30	0.54	275	85	<5	0.95	34	3	44	6371	1.60	<10	0.08	573	33	0.02	7	280	5350	55	<20	143	<0.01	<10	13	10	1	8409
106		>30	0.54	275	75	<5	0.95	34	3	44	6306	1.61	<10	0.08	571	35	0.02	7	270	5322	55	<20	144	<0.01	<10	13	10	<1	8377

**ECO TECH LABORATORY LTD.**  
 Jutta Jealous  
 B.C. Certified Assayer

J/sa  
 2106  
 LS/06



**Assay Certificate**

**6V-2597-RA1**

Company: **Levon Resources**  
 Project: **LZ (Nov 17.06)**  
 Attn: **C.Kauss**

Dec-03-06

We hereby certify the following assay of 24 core samples submitted Nov-24-06

Sample Name	Au g/tonne	Au-check g/tonne
143689	<0.01	<0.01
143690	0.01	
143691	<0.01	
143692	<0.01	
143693	<0.01	L2-06-02
143694	<0.01	
143695	<0.01	
143696	0.01	
143697	0.01	
143698	0.01	
143699	<0.01	
143700	<0.01	
143701	0.02	
143702	<0.01	
143703	<0.01	L2-06-03
143704	<0.01	
143705	<0.01	
143706	<0.01	
143707	<0.01	
143708	<0.01	<0.01
143709	5.41	
143710	3.39	
143711	0.08	
143712	0.03	
*OxH52	1.32	
*BLANK	<0.01	

Certified by



**Assay Certificate**

6V-2597-RA2

Company: **Levon Resources**  
 Project: **LZ (Nov 17,06)**  
 Attn: **C.Kauss**

Dec-03-06

We hereby certify the following assay of 24 core samples submitted Nov-24-06

Sample Name	Au g/tonne	Au-check g/tonne
143713	0.05	0.05
143714	<0.01	
143715	<0.01	
143716	<0.01	
143717	0.07	
143718	<0.01	
143719	0.30	LZ-06-03
143720	1.90	
143721	1.52	
143722	0.05	
143723	0.07	
143724	<0.01	
143725	<0.01	
143726	<0.01	
143727	<0.01	
143728	<0.01	
143729	<0.01	LZ-06-04
143730	0.01	
143731	<0.01	
143732	<0.01	<0.01
143733	<0.01	
143734	0.01	
143735	<0.01	
143736	<0.01	
*OxH52	1.29	
*BLANK	<0.01	

Certified by



**Assayers Canada**  
8282 Sherbrooke St.  
Vancouver, B.C.  
V5X 4R6  
Tel: (604) 327-3436  
Fax: (604) 327-3423

**Assay Certificate**

**6V-2597-RA3**

**Dec-03-06**

Company: **Levon Resources**  
Project: **LZ (Nov 17,06)**  
Attn: **C.Kauss**

We hereby certify the following assay of 24 core samples submitted Nov-24-06

<b>Sample Name</b>	<b>Au g/tonne</b>	<b>Au-check g/tonne</b>
143737	0.01	<0.01
143738	<0.01	
143739	<0.01	
143740	<0.01	LZ-06-04
143741	<0.01	
143742	<0.01	
143743	<0.01	
143744	0.01	
143745	<0.01	
143746	<0.01	
143747	<0.01	
143748	<0.01	
143749	<0.01	
143750	<0.01	LZ-06-05
143751	<0.01	
143752	<0.01	
143753	<0.01	
143754	<0.01	
143755	<0.01	
143756	<0.01	<0.01
143757	<0.01	
143758	<0.01	
143759	<0.01	
143760	<0.01	
*OxH52	1.31	
*BLANK	<0.01	

Certified by



**Assayers Canada**  
8282 Sherbrooke St.  
Vancouver, B.C.  
V5X 4R6  
Tel: (604) 327-3436  
Fax: (604) 327-3423

**Assay Certificate**

**6V-2597-RA4**

Company: **Levon Resources**  
Project: **LZ (Nov 17,06)**  
Att: **C.Kauss**

Dec-03-06

We hereby certify the following assay of 7 core samples  
submitted Nov-24-06

<b>Sample Name</b>	<b>Au g/tonne</b>	<b>Au-check g/tonne</b>
143761	0.14	0.13
143762	4.21	
143763	0.30	
143764	1.03	
143765	0.75	LZ-06-05
143766	0.28	
143767	0.26	
*OxH52	1.32	
*BLANK	<0.01	

Certified by

# Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 6V2597R1

Date : Dec-03-06

## Levon Resources

Attention: C. Kauss

Project: L.Z. (Nov 17,06)

Sample type:

## Multi-Element ICP-AES Analysis

Aqua Regia Digestion

Sample Number	Ag ppm	Al %	As ppm	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	Hg ppm	K %	La ppm	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	S %	Sb ppm	Sc ppm	Sr ppm	Th ppm	Ti %	Tl ppm	U ppm	V ppm	W ppm	Zn ppm	Zr ppm
143689	<0.2	3.25	<5	27	0.8	<5	6.25	<1	47	162	48	5.74	<1	0.09	11	3.14	1667	3	0.11	212	1185	<2	0.08	11	13	95	<5	0.48	<10	21	122	<10	75	41
143690	<0.2	1.99	9	20	0.7	<5	8.43	<1	22	111	24	3.73	<1	0.07	<10	1.11	745	7	0.04	66	778	<2	0.52	<5	10	93	<5	0.24	<10	52	82	<10	43	21
143691	<0.2	2.57	38	44	0.7	<5	13.89	1	47	108	54	4.43	<1	0.15	11	0.76	2079	9	0.05	115	1024	<2	1.42	10	17	124	6	0.46	<10	35	117	<10	56	43
143692	0.4	2.91	<5	25	0.8	<5	8.84	<1	33	119	23	4.38	<1	0.04	<10	2.84	1108	3	0.07	110	692	<2	2.01	6	12	72	<5	0.36	<10	46	115	<10	45	25
143693	<0.2	4.20	<5	19	<0.5	<5	4.73	<1	54	315	61	6.27	<1	0.08	<10	2.58	1218	<2	0.11	201	475	<2	0.22	13	30	69	<5	0.42	<10	29	194	<10	96	35
143694	<0.2	3.48	<5	35	0.6	<5	6.49	<1	50	222	68	5.96	<1	0.10	10	4.83	1410	3	0.08	369	776	<2	0.19	<5	11	162	<5	0.03	<10	37	74	<10	73	9
143695	<0.2	0.78	8	16	<0.5	<5	3.16	<1	14	80	36	2.35	<1	0.05	<10	1.05	482	10	0.02	78	376	4	0.35	<5	3	62	<5	<0.01	<10	23	28	<10	45	3
143696	<0.2	0.16	56	35	<0.5	<5	2.15	3	16	79	143	2.88	<1	0.08	<10	0.96	529	34	0.02	72	612	13	1.01	8	2	55	<5	<0.01	<10	15	25	<10	142	4
143697	<0.2	3.20	<5	49	0.5	<5	3.06	<1	48	130	78	6.67	<1	0.16	<10	1.99	1162	2	0.05	119	863	<2	0.02	5	16	63	<5	0.26	<10	23	95	<10	142	23
143698	<0.2	3.04	<5	36	0.5	<5	5.30	<1	42	126	63	6.28	<1	0.13	12	2.21	1422	3	0.04	112	1130	<2	0.01	<5	17	116	<5	0.01	<10	25	96	<10	104	6
143699	<0.2	4.76	<5	22	0.6	<5	5.09	<1	56	182	46	6.72	<1	0.09	<10	3.22	1508	2	0.07	144	1035	<2	0.03	8	21	79	<5	0.34	<10	30	160	<10	96	36
143700	<0.2	0.82	15	51	0.5	<5	3.99	<1	50	58	41	7.37	<1	0.27	<10	1.69	1597	2	0.07	93	1406	7	3.24	5	18	83	<5	<0.01	<10	17	62	<10	127	6
143701	<0.2	0.55	116	27	<0.5	<5	3.27	3	48	30	76	6.81	<1	0.27	<10	1.23	1254	2	0.08	99	1122	5	>5.00	13	15	76	<5	<0.01	<10	20	23	<10	148	5
143702	<0.2	1.58	49	99	<0.5	<5	4.00	1	26	69	29	4.81	<1	0.20	<10	1.93	925	3	0.09	55	907	<2	2.33	7	10	106	<5	<0.01	<10	30	60	<10	80	4
143703	<0.2	1.76	<5	102	<0.5	<5	3.74	<1	14	75	13	3.29	<1	0.11	<10	1.88	691	3	0.09	31	750	<2	0.06	<5	7	111	<5	0.02	<10	23	81	<10	63	5
143704	<0.2	1.88	<5	76	<0.5	<5	3.75	<1	15	75	12	3.45	<1	0.14	10	2.02	683	2	0.10	37	806	<2	0.02	<5	8	119	<5	0.01	<10	27	77	<10	69	4
143705	<0.2	1.89	<5	26	<0.5	<5	3.87	<1	15	66	13	3.20	<1	0.13	<10	2.00	648	3	0.10	34	788	<2	0.03	<5	7	134	<5	0.01	<10	26	62	<10	71	4
143706	<0.2	1.68	<5	28	<0.5	<5	3.16	<1	14	66	11	3.12	<1	0.10	<10	1.89	621	2	0.09	30	735	<2	0.01	<5	7	114	<5	0.01	<10	19	69	<10	67	4
143707	<0.2	0.71	<5	53	<0.5	<5	3.74	<1	11	27	10	2.86	<1	0.13	<10	1.62	653	3	0.07	20	656	5	0.03	<5	6	178	<5	<0.01	<10	23	35	<10	57	3
143708	<0.2	1.84	<5	396	0.5	<5	4.24	<1	28	101	38	4.91	<1	0.17	<10	2.21	1448	2	0.09	84	919	2	0.05	7	12	150	<5	<0.01	<10	<10	89	<10	93	5
143709	0.4	1.49	5380	66	<0.5	<5	3.85	140	41	95	62	6.07	<1	0.24	<10	1.99	1688	2	0.06	112	878	5	2.14	74	15	89	<5	<0.01	<10	<10	73	<10	132	5
143710	0.2	0.50	1793	41	<0.5	<5	2.81	46	47	45	78	6.04	<1	0.18	<10	1.14	1258	2	0.06	101	941	8	4.25	32	12	75	<5	<0.01	<10	<10	42	<10	126	5
143711	<0.2	0.57	366	31	<0.5	<5	3.21	9	44	52	62	6.72	<1	0.23	<10	1.74	1564	2	0.06	88	986	7	2.63	19	14	83	<5	<0.01	<10	14	67	<10	146	5
143712	<0.2	0.76	235	59	0.5	<5	3.27	6	43	72	100	6.79	<1	0.21	<10	2.01	1563	3	0.06	107	944	8	1.46	22	16	91	5	<0.01	<10	25	89	<10	153	5
143713	<0.2	0.32	357	38	<0.5	<5	4.11	9	35	26	46	5.56	<1	0.17	<10	1.75	1123	4	0.08	77	897	12	3.93	21	11	101	<5	<0.01	<10	33	34	<10	85	5
143714	<0.2	0.71	8	282	<0.5	<5	4.95	<1	12	34	17	3.06	<1	0.15	<10	1.97	751	5	0.10	29	753	3	0.21	<5	8	140	5	<0.01	<10	38	47	<10	48	3
143715	<0.2	0.33	5	91	<0.5	<5	4.75	<1	13	23	12	3.03	<1	0.12	<10	1.99	645	3	0.05	20	702	9	0.23	<5	8	180	7	<0.01	<10	45	39	<10	64	4
143716	<0.2	0.56	<5	36	<0.5	<5	3.39	<1	10	47	7	2.72	<1	0.14	10	1.49	624	3	0.06	18	728	7	0.03	<5	8	120	6	<0.01	<10	35	35	<10	51	4
143717	<0.2	0.64	305	117	<0.5	<5	3.41	8	13	43	12	2.78	<1	0.14	<10	1.62	677	3	0.06	25	749	5	0.30	<5	8	123	6	<0.01	<10	30	42	<10	60	3
143718	<0.2	0.45	6	54	<0.5	<5	4.13	<1	13	45	13	2.87	<1	0.14	<10	1.74	658	4	0.06	23	747	6	0.06	<5	6	174	9	0.01	<10	47	50	<10	60	4

A .5 gm sample is digested with 5 ml 3:1 HCl/HNO3 at 95°C for 2 hours and diluted to 25ml.



**Levon Resources**

Attention: C.Kauss

Project: L.Z. (Nov 17.06)

Sample type:

**Assayers Canada**

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 6V2597RJ

Date : Dec-03-06

**Multi-Element ICP-AES Analysis**

Aqua Regia Digestion

Sample Number	Ag ppm	Al %	As ppm	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	Hg ppm	K %	La ppm	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	S %	Sb ppm	Sc ppm	Sr ppm	Th ppm	Ti %	Tl ppm	U ppm	V ppm	W ppm	Zn ppm	Zr ppm
143719	<0.2	0.35	726	78	<0.5	<5	4.20	18	14	38	11	3.24	<1	0.15	<10	1.97	640	3	0.05	30	765	6	0.63	14	7	156	10	<0.01	<10	52	41	<10	65	4
143720	0.4	0.32	4767	51	<0.5	<5	4.31	120	15	25	15	3.37	<1	0.19	<10	1.98	740	4	0.05	31	681	6	1.23	32	7	125	10	<0.01	<10	49	26	<10	65	4
143721	0.2	0.35	1884	48	<0.5	<5	4.47	47	14	24	10	3.48	<1	0.18	<10	2.14	744	4	0.06	32	453	7	1.77	22	7	141	9	<0.01	<10	48	23	<10	60	4
143722	<0.2	0.35	430	79	<0.5	<5	4.04	10	27	31	51	4.60	1	0.19	<10	1.90	926	4	0.07	59	644	5	1.96	35	12	117	6	<0.01	<10	38	32	<10	94	5
143723	<0.2	0.27	385	31	<0.5	<5	2.08	10	29	46	90	5.84	1	0.20	<10	1.26	733	7	0.06	97	643	7	2.56	37	15	70	5	<0.01	<10	34	34	<10	166	6
143724	<0.2	0.23	51	98	<0.5	<5	2.85	1	17	65	43	3.40	<1	0.13	<10	2.21	695	7	0.04	95	228	8	0.43	10	7	104	6	<0.01	<10	26	34	<10	68	5
143725	<0.2	2.32	8	51	0.9	<5	2.97	<1	49	96	75	6.98	<1	0.21	13	1.59	1102	2	0.06	106	1085	<2	0.30	<5	13	107	<5	0.05	<10	36	91	<10	151	10
143726	<0.2	2.90	18	34	0.5	<5	3.18	<1	57	154	62	7.13	<1	0.14	11	2.20	1147	2	0.06	115	1260	<2	1.05	10	15	73	<5	0.39	<10	37	117	<10	147	29
143727	<0.2	3.22	35	35	0.6	<5	3.75	1	48	182	80	7.15	<1	0.12	<10	2.34	1022	2	0.07	130	874	<2	0.52	7	17	88	7	0.20	<10	50	110	<10	155	26
143728	<0.2	4.09	34	22	0.5	<5	3.46	<1	52	255	83	7.55	13	0.07	<10	3.44	1418	2	0.06	164	1005	<2	0.25	6	18	73	<5	0.15	<10	31	153	<10	157	18
143729	<0.2	3.68	69	18	0.5	<5	3.02	1	54	213	47	6.93	1	0.09	<10	2.94	1352	2	0.07	130	1008	<2	0.53	13	15	66	5	0.33	<10	29	142	<10	135	29
143730	<0.2	3.56	79	16	0.6	<5	4.24	2	48	168	49	7.05	1	0.09	12	2.70	1406	2	0.07	115	1417	<2	0.72	6	14	74	6	0.22	<10	33	139	<10	125	23
143731	<0.2	3.50	34	14	0.6	<5	6.67	<1	43	183	31	6.04	2	0.07	10	3.38	1687	3	0.07	122	1026	<2	0.37	12	15	95	8	0.29	<10	43	141	<10	97	24
143732	<0.2	3.63	78	11	<0.5	<5	5.17	2	46	198	45	6.72	1	0.06	11	3.48	1469	3	0.07	137	1198	<2	0.99	7	15	74	5	0.12	<10	36	152	<10	84	12
143733	<0.2	3.94	53	14	0.6	<5	4.63	1	48	188	44	6.66	1	0.04	10	3.50	1198	2	0.14	124	1211	<2	0.83	14	18	87	6	0.29	<10	44	168	<10	69	28
143734	<0.2	2.91	49	25	0.7	<5	3.83	1	49	129	76	6.86	<1	0.14	10	2.07	894	2	0.08	101	966	<2	1.13	10	14	64	5	0.23	<10	46	114	<10	65	20
143735	<0.2	3.92	31	18	0.7	<5	3.19	<1	55	163	20	7.85	<1	0.10	14	2.77	1291	2	0.13	108	1756	<2	0.84	9	17	70	8	0.28	<10	42	149	<10	106	23
143736	<0.2	3.20	71	25	0.6	<5	2.98	1	50	124	52	7.77	<1	0.23	15	2.01	953	<2	0.07	102	1721	<2	1.30	5	13	60	6	0.16	<10	44	116	<10	91	15
143737	<0.2	3.45	61	26	0.6	<5	2.94	1	55	204	60	7.90	<1	0.17	13	2.49	1184	<2	0.08	144	1307	<2	1.15	7	13	70	<5	0.13	<10	37	113	<10	110	13
143738	<0.2	3.32	34	26	0.6	<5	2.26	1	51	132	70	6.87	<1	0.22	12	2.11	1273	<2	0.10	117	1403	<2	0.40	5	11	68	<5	0.17	<10	12	109	<10	116	18
143739	<0.2	2.99	45	25	0.6	<5	2.22	1	55	132	59	7.28	<1	0.18	14	2.03	1192	<2	0.08	114	1231	<2	0.87	8	12	77	<5	0.18	<10	19	99	<10	115	18
143740	<0.2	3.25	35	32	0.7	<5	2.86	1	58	129	60	7.32	<1	0.27	12	2.13	1463	<2	0.06	129	1402	<2	0.62	8	13	79	<5	0.32	<10	14	111	<10	144	32
143741	<0.2	3.02	20	34	0.7	<5	3.48	<1	62	122	51	7.32	<1	0.23	12	2.06	1407	2	0.06	137	1425	<2	0.23	14	14	91	5	0.40	<10	22	121	<10	151	37
143742	<0.2	3.31	19	40	0.5	<5	5.36	1	51	169	52	6.88	1	0.18	<10	2.61	1543	3	0.07	128	1147	<2	0.20	8	15	104	5	0.21	<10	26	134	<10	155	23
143743	<0.2	4.25	17	72	0.6	<5	1.58	<1	53	154	74	7.58	<1	0.18	<10	3.88	1359	<2	0.06	140	1147	<2	0.28	6	13	81	<5	0.21	<10	11	108	<10	154	17
143744	<0.2	3.65	45	79	0.7	<5	1.98	1	40	114	52	7.33	1	0.14	15	2.63	1057	<2	0.13	100	2064	<2	1.24	7	12	84	<5	0.13	<10	18	135	<10	127	14
143745	<0.2	4.70	36	121	0.6	<5	5.79	1	47	296	48	5.88	3	0.03	<10	4.71	1099	3	0.23	234	839	<2	0.82	8	19	195	5	0.16	<10	37	161	<10	101	18
143746	<0.2	2.44	27	95	<0.5	<5	4.26	1	18	105	45	3.66	2	0.12	<10	2.73	822	5	0.06	80	783	<2	0.92	<5	7	144	<5	<0.01	<10	28	72	<10	51	4
143747	<0.2	2.30	14	232	<0.5	<5	3.44	<1	16	78	48	3.50	2	0.15	<10	2.36	586	3	0.06	43	822	<2	0.41	<5	7	155	<5	<0.01	<10	26	64	<10	52	4
143748	<0.2	1.96	12	493	<0.5	<5	4.53	<1	15	70	37	3.39	1	0.16	10	1.87	708	3	0.05	36	784	<2	0.29	<5	7	187	6	<0.01	<10	32	59	<10	57	4

A 5 gm sample is digested with 5 ml 3:1 HCl/HNO3 at 95°C for 2 hours and diluted to 25ml.



**Levon Resources**

Attention: C. Kauss

Project: LZ (Nov 17.06)

Sample type:

**Assayers Canada**

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 6V2597RJ


Date : Dec-03-06

**Multi-Element ICP-AES Analysis**

Aqua Regia Digestion

Sample Number	Ag ppm	Al %	As ppm	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	Hg ppm	K %	La ppm	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	S %	Sb ppm	Sc ppm	Sr ppm	Th ppm	Ti %	Tl ppm	U ppm	V ppm	W ppm	Zn ppm	Zr ppm
143749	<0.2	1.89	<5	191	<0.5	<5	3.81	<1	14	77	12	3.24	<1	0.17	<10	1.75	643	3	0.06	33	748	<2	0.09	<5	7	157	5	<0.01	<10	24	62	<10	60	4
143750	<0.2	1.85	<5	248	<0.5	<5	2.93	<1	13	83	11	3.30	1	0.07	<10	1.92	657	3	0.06	29	725	<2	0.02	<5	7	120	<5	<0.01	<10	22	72	<10	67	4
143751	<0.2	1.88	<5	313	<0.5	<5	2.60	<1	14	86	12	3.47	<1	0.05	<10	2.06	651	2	0.07	30	753	<2	0.01	<5	7	115	<5	<0.01	<10	23	86	<10	68	4
143752	<0.2	1.78	<5	271	<0.5	<5	2.51	<1	13	87	11	3.39	<1	0.07	<10	1.93	633	2	0.07	29	725	<2	0.04	<5	7	110	<5	<0.01	<10	22	81	<10	65	4
143753	<0.2	1.75	<5	248	<0.5	<5	2.44	<1	13	89	12	3.36	1	0.06	<10	1.90	608	2	0.07	28	721	<2	0.04	<5	8	114	<5	<0.01	<10	22	82	<10	64	4
143754	<0.2	1.65	<5	411	<0.5	<5	3.64	<1	13	85	12	3.19	<1	0.09	<10	1.69	701	2	0.06	29	711	<2	0.10	<5	7	149	5	<0.01	<10	24	71	<10	59	4
143755	<0.2	1.60	<5	215	<0.5	<5	5.33	<1	12	78	10	3.10	<1	0.08	11	1.70	926	3	0.05	27	683	<2	0.03	<5	6	139	<5	<0.01	<10	23	66	<10	56	3
143756	<0.2	1.79	<5	167	<0.5	<5	2.33	<1	14	90	10	3.38	<1	0.04	<10	2.04	616	2	0.06	29	722	<2	0.02	<5	7	102	<5	<0.01	<10	18	88	<10	67	4
143757	<0.2	2.05	63	64	<0.5	<5	4.20	1	48	422	39	3.55	<1	0.04	<10	3.91	798	3	0.07	679	447	<2	0.64	8	6	182	<5	0.02	<10	24	62	<10	58	3
143758	<0.2	4.15	11	34	0.5	<5	3.43	<1	53	246	51	5.87	<1	0.05	<10	4.81	1003	2	0.23	249	722	<2	0.41	15	11	168	<5	0.31	<10	21	102	<10	81	23
143759	<0.2	3.01	<5	103	0.7	<5	5.01	<1	42	109	41	6.51	<1	0.15	23	2.45	1696	3	0.05	145	2000	<2	0.02	<5	11	160	6	<0.01	<10	15	83	<10	103	7
143760	<0.2	2.21	<5	64	0.5	<5	7.30	<1	38	109	81	5.43	<1	0.14	12	1.61	1193	3	0.06	124	1169	<2	0.06	<5	12	214	<5	0.01	<10	37	69	<10	96	7
143761	<0.2	0.34	96	61	<0.5	<5	2.61	3	14	35	87	3.35	<1	0.21	<10	1.17	533	6	0.04	72	457	11	2.36	24	6	60	<5	<0.01	<10	18	13	<10	82	3
143762	0.6	0.72	2258	165	<0.5	<5	4.10	65	14	34	17	3.64	<1	0.23	<10	1.85	784	3	0.10	58	533	2	1.27	17	10	132	<5	<0.01	<10	23	38	<10	61	3
143763	0.6	1.30	1445	117	0.5	<5	6.15	42	45	82	83	6.01	<1	0.24	<10	2.70	1190	4	0.10	159	823	<2	1.89	39	22	127	<5	<0.01	<10	38	65	<10	79	7
143764	0.2	0.44	2034	36	0.5	<5	5.10	58	41	32	47	6.09	<1	0.23	<10	1.95	1042	3	0.10	104	950	4	>5.00	57	18	114	<5	<0.01	<10	21	34	<10	108	5
143765	<0.2	0.43	1142	49	0.5	<5	4.91	32	43	24	53	5.95	2	0.28	<10	2.16	1289	3	0.09	118	984	4	4.11	52	16	108	<5	<0.01	<10	<10	28	<10	139	5
143766	<0.2	1.06	88	175	0.5	<5	5.95	2	40	67	46	5.44	2	0.26	13	3.06	1300	3	0.11	157	1406	<2	1.11	21	17	163	<5	<0.01	<10	<10	70	<10	67	6
143767	<0.2	1.21	85	91	<0.5	<5	5.30	2	41	57	55	6.21	4	0.25	<10	2.24	1305	3	0.11	95	958	<2	2.09	8	19	99	<5	<0.01	<10	10	87	<10	98	6

A .5 gm sample is digested with 5 ml 3:1 HCl/HNO3 at 95°C for 2 hours and diluted to 25ml.

Signed: 

Certificate Number	Sample Name	Assay Au g/tonne	Assay Au-Check g/tonne	
6V2598RA	143768	<0.01	<0.01	L2-06-05
6V2598RA	143769	<0.01		
6V2598RA	143770	<0.01		
6V2598RA	143771	<0.01		
6V2598RA	143772	<0.01		
6V2598RA	143773	<0.01		
6V2598RA	143774	<0.01		
6V2598RA	143775	<0.01		
6V2598RA	143776	<0.01		
6V2598RA	143777	<0.01	<0.01	
6V2598RA	143778	<0.01		L2-06-06
6V2598RA	143779	0.03		
6V2598RA	143780	<0.01		
6V2598RA	143781	0.09		
6V2598RA	143782	<0.01		
6V2598RA	143783	<0.01		
6V2598RA	143784	0.01		
6V2598RA	143785	<0.01		
6V2598RA	143786	0.29		
6V2598RA	143787	0.11	0.1	
6V2598RA	143788	0.12		
6V2598RA	143789	0.03		
6V2598RA	143790	<0.01		
6V2598RA	143791	<0.01		
6V2598RA	*OXH-52	1.32		
6V2598RA	*BLANK	<0.01		

Certificate Number	Sample Name	ICP Ag ppm	ICP Al %	ICP As ppm	ICP Ba ppm	ICP Be ppm	ICP Bi ppm	ICP Ca %	ICP Cd ppm	ICP Co ppm	ICP Cr ppm	ICP Cu ppm	ICP Fe %	ICP Hg ppm	ICP K %
6V2598RJ	143768	<0.2	1.88	<5	33	<0.5	<5	4.98	<1	38	65	80	5.59	1	0.16
6V2598RJ	143769	<0.2	2.27	<5	28	<0.5	<5	3.22	<1	45	108	36	6.6	<1	0.16
6V2598RJ	143770	<0.2	1.64	<5	145	<0.5	<5	3.71	<1	13	58	13	2.97	<1	0.12
6V2598RJ	143771	<0.2	1.75	<5	66	<0.5	<5	3.89	<1	14	56	17	2.91	<1	0.15
6V2598RJ	143772	<0.2	1.45	<5	48	<0.5	<5	2.8	<1	12	58	11	2.81	<1	0.1
6V2598RJ	143773	<0.2	1.55	<5	455	<0.5	<5	2.18	<1	13	76	11	3.02	<1	0.05
6V2598RJ	143774	<0.2	1.58	<5	143	<0.5	<5	1.82	<1	15	74	10	3.09	<1	0.05
6V2598RJ	143775	<0.2	1.55	<5	78	<0.5	<5	1.89	<1	15	82	13	3.04	<1	0.06
6V2598RJ	143776	<0.2	1.47	<5	66	<0.5	<5	1.81	<1	16	76	12	3.04	<1	0.05
6V2598RJ	143777	<0.2	1.39	<5	59	<0.5	<5	1.21	<1	16	74	14	2.88	<1	0.05
6V2598RJ	143778	<0.2	1.55	<5	79	<0.5	<5	1.92	<1	17	76	15	3.13	<1	0.05
6V2598RJ	143779	<0.2	1.8	<5	73	<0.5	<5	1.96	<1	18	92	15	3.39	<1	0.06
6V2598RJ	143780	<0.2	2.51	8	66	<0.5	<5	2.7	<1	22	146	16	3.65	<1	0.04
6V2598RJ	143781	<0.2	2.53	18	381	<0.5	<5	11.44	<1	62	713	25	3.77	<1	<0.01
6V2598RJ	143782	<0.2	5.14	<5	533	<0.5	<5	6.87	<1	58	441	53	6.59	<1	<0.01
6V2598RJ	143783	<0.2	4.91	<5	371	<0.5	<5	3.97	<1	53	326	61	6.9	<1	0.04
6V2598RJ	143784	<0.2	3.54	<5	912	0.5	<5	4.27	<1	52	178	45	6.59	<1	0.12
6V2598RJ	143785	<0.2	4.12	<5	189	0.9	<5	3.48	<1	55	271	33	6.35	<1	0.1
6V2598RJ	143786	<0.2	0.88	767	40	<0.5	<5	4.83	21	35	58	52	5.17	<1	0.2
6V2598RJ	143787	<0.2	0.37	1164	36	0.5	<5	4.44	32	34	16	40	7.08	<1	0.24
6V2598RJ	143788	<0.2	0.37	459	46	0.5	<5	5.13	12	40	27	58	6.71	<1	0.24
6V2598RJ	143789	<0.2	0.88	664	32	0.5	<5	4.24	18	48	48	652	6.51	1	0.19
6V2598RJ	143790	<0.2	0.77	21	41	<0.5	<5	3	1	21	66	43	4.41	<1	0.13
6V2598RJ	143791	<0.2	1.12	41	53	<0.5	<5	2.58	1	45	333	37	3.69	<1	0.13
6V2598RJ	143792	<0.2	1.39	93	58	<0.5	<5	2.45	3	27	225	43	3.84	<1	0.13
6V2598RJ	143793	<0.2	1.19	12	144	<0.5	<5	1.85	1	18	64	64	3.85	<1	0.14
6V2598RJ	143794	<0.2	1.73	8	111	0.5	<5	1.87	<1	24	129	50	4.14	<1	0.18
6V2598RJ	143795	<0.2	1.48	10	153	<0.5	<5	2.12	1	19	99	43	4.01	<1	0.14
6V2598RJ	143796	<0.2	1.35	10	97	0.5	<5	2.25	<1	22	126	52	4.21	<1	0.13
6V2598RJ	143797	<0.2	1.4	8	61	<0.5	<5	1.85	<1	30	237	52	3.31	<1	0.11
6V2598RJ	143798	<0.2	0.88	25	90	<0.5	<5	1.84	1	19	164	37	3.22	<1	0.11
6V2598RJ	143799	<0.2	0.94	17	63	<0.5	<5	1.45	1	16	90	48	3.5	<1	0.16
6V2598RJ	143800	<0.2	1.57	16	105	<0.5	<5	3.23	<1	83	814	45	4.15	<1	0.03
6V2598RJ	143801	<0.2	0.26	<5	23	<0.5	<5	4.48	<1	89	666	19	3.88	<1	0.01
6V2598RJ	143802	<0.2	0.38	357	26	<0.5	<5	5.12	9	48	203	29	4.78	<1	0.08
6V2598RJ	143803	<0.2	1.16	318	291	<0.5	<5	4.72	9	22	79	23	3.53	<1	0.13
6V2598RJ	143804	<0.2	1.28	8	687	<0.5	<5	4.04	<1	14	55	18	3.32	<1	0.21
6V2598RJ	143805	<0.2	1.8	<5	275	<0.5	<5	2.99	<1	16	77	17	3.53	<1	0.14
6V2598RJ	143806	<0.2	1.83	128	567	<0.5	<5	4.45	3	30	224	23	4.08	<1	0.08
6V2598RJ	143807	<0.2	2.3	145	69	<0.5	<5	5.45	4	48	333	49	5.68	<1	0.12
6V2598RJ	143808	<0.2	1.2	24	150	0.5	<5	6.57	<1	46	85	42	5.64	<1	0.19
6V2598RJ	143809	<0.2	0.33	3604	36	<0.5	<5	5.55	102	38	44	25	5.62	<1	0.17
6V2598RJ	143810	<0.2	0.33	3175	32	<0.5	<5	6.18	90	36	30	39	6.01	<1	0.21
6V2598RJ	143811	<0.2	2.12	52	25	<0.5	<5	3.86	1	45	142	54	6.86	<1	0.12

ICP La ppm	ICP Mg %	ICP Mn ppm	ICP Mo ppm	ICP Na %	ICP Ni ppm	ICP P ppm	ICP Pb ppm	ICP S %	ICP Sb ppm	ICP Sc ppm	ICP Sr ppm	ICP Th ppm	ICP Ti %	ICP Tl ppm	ICP U ppm	ICP V ppm	ICP W ppm	ICP Zn ppm	ICP Zr ppm
<10	2.17	1509	3	0.14	95	816	<2	0.08	<5	21	103	<5	<0.01	<10	<10	109	<10	99	5
<10	1.69	1145	<2	0.14	133	884	<2	<0.01	<5	23	75	<5	<0.01	<10	<10	124	<10	139	6
<10	1.6	623	2	0.07	29	712	2	<0.01	<5	7	206	<5	<0.01	<10	<10	67	<10	61	6
10	1.55	607	2	0.08	31	682	3	<0.01	<5	6	231	<5	<0.01	<10	14	62	<10	59	5
10	1.55	531	2	0.08	23	674	<2	<0.01	<5	6	71	<5	0.01	<10	<10	64	<10	54	5
<10	1.78	541	2	0.1	27	689	<2	0.01	<5	8	64	<5	0.04	<10	<10	83	<10	54	6
<10	1.82	519	2	0.15	27	716	<2	<0.01	<5	9	53	<5	0.09	<10	<10	89	<10	53	9
<10	1.73	547	<2	0.15	29	737	<2	<0.01	<5	8	55	<5	0.09	<10	<10	88	<10	53	10
<10	1.93	534	<2	0.09	30	751	<2	<0.01	<5	9	43	<5	0.13	<10	<10	92	<10	53	13
<10	1.95	483	<2	0.11	29	769	<2	<0.01	<5	8	43	<5	0.17	<10	<10	87	<10	47	18
<10	1.94	580	<2	0.1	29	724	4	0.01	<5	9	47	<5	0.16	<10	<10	98	<10	54	14
<10	2.42	718	2	0.1	37	779	<2	0.02	<5	9	46	<5	0.13	<10	<10	102	<10	56	13
<10	3.21	687	3	0.15	127	714	<2	0.08	<5	10	99	<5	0.08	<10	<10	109	<10	57	8
<10	4.4	1297	4	0.07	905	281	<2	0.24	10	11	241	<5	<0.01	<10	38	68	<10	41	3
<10	6.78	1158	2	0.06	488	445	<2	0.16	6	19	197	<5	<0.01	<10	33	145	<10	70	6
<10	7.06	1029	<2	0.07	347	615	<2	0.06	<5	20	158	<5	0.02	<10	22	154	<10	82	8
<10	3.62	1084	<2	0.08	162	961	<2	0.04	11	19	155	<5	0.35	<10	16	136	<10	102	27
20	5.22	1165	<2	0.09	261	1798	<2	0.05	12	15	102	<5	0.4	<10	<10	118	<10	82	34
<10	2.55	1088	2	0.09	117	822	5	2.8	22	18	148	<5	<0.01	<10	11	51	<10	85	5
<10	1.76	1345	2	0.1	64	1423	5	>5.00	26	17	104	<5	<0.01	<10	12	25	<10	116	7
<10	2.07	1516	2	0.09	78	1210	3	2.75	17	18	108	<5	<0.01	<10	24	44	<10	134	6
<10	2.24	1495	2	0.08	129	1221	3	4.66	59	20	113	<5	<0.01	<10	16	60	<10	111	6
<10	2.64	922	4	0.05	123	689	3	0.44	<5	9	152	<5	<0.01	<10	20	38	<10	96	4
<10	2.59	814	4	0.05	652	447	4	0.52	9	9	132	<5	<0.01	<10	13	38	<10	84	4
<10	2.88	805	6	0.05	278	557	4	0.56	7	9	109	<5	<0.01	<10	12	49	<10	102	4
10	2.12	774	5	0.05	67	1043	2	0.5	<5	9	77	<5	<0.01	<10	<10	60	<10	120	4
11	2.7	814	5	0.05	155	726	2	0.44	<5	9	91	<5	<0.01	<10	13	54	<10	97	4
12	3	786	5	0.05	141	1316	3	0.47	<5	8	98	<5	<0.01	<10	<10	50	<10	128	4
<10	3.48	875	5	0.05	189	683	<2	0.43	6	9	116	<5	<0.01	<10	<10	57	<10	87	4
<10	3.72	715	4	0.04	429	631	2	0.35	<5	7	95	<5	<0.01	<10	10	40	<10	70	3
<10	3.27	630	5	0.04	212	536	2	0.51	16	6	102	<5	<0.01	<10	<10	31	<10	72	3
<10	2.07	716	5	0.04	109	561	5	0.54	<5	7	69	<5	<0.01	<10	<10	29	<10	102	4
<10	7.83	847	7	0.04	1402	333	<2	0.48	12	9	155	<5	<0.01	<10	32	53	<10	63	3
<10	9.88	601	4	0.02	1706	39	2	0.33	10	6	175	<5	<0.01	<10	40	18	<10	20	3
<10	8.53	828	5	0.03	752	264	3	0.35	146	9	204	<5	<0.01	<10	45	29	<10	46	4
<10	3.27	694	4	0.06	176	561	4	0.65	45	8	181	<5	<0.01	<10	35	58	<10	77	3
<10	2.39	772	4	0.07	36	632	2	0.18	6	7	120	<5	<0.01	<10	28	50	<10	66	3
<10	2.62	707	3	0.08	38	654	<2	0.06	<5	8	103	<5	<0.01	<10	23	77	<10	71	3
<10	4.34	796	4	0.11	367	577	<2	0.25	12	11	205	<5	<0.01	<10	34	89	<10	70	5
<10	5.51	1085	4	0.1	447	497	<2	0.76	19	16	253	<5	<0.01	<10	38	89	<10	70	5
<10	3.79	1139	3	0.1	205	779	<2	0.7	9	19	210	<5	<0.01	<10	40	67	<10	72	6
<10	2.42	1111	4	0.07	143	747	4	4.66	61	12	148	<5	<0.01	<10	34	29	<10	75	5
<10	2.75	1072	4	0.08	109	909	4	4.1	59	16	130	<5	<0.01	<10	35	30	<10	81	5
<10	3.86	1230	2	0.09	168	913	<2	0.45	21	20	95	<5	<0.01	<10	25	101	<10	110	6

Certificate Number	Sample Name	Assay	Assay
		Au g/tonne	Au-Check g/tonne
6V2652RA	143884	0.01	<0.01
6V2652RA	143885	<0.01	
6V2652RA	143886	0.01	
6V2652RA	143887	0.03	
6V2652RA	143888	0.01	
6V2652RA	143889	0.01	
6V2652RA	143890	0.01	
6V2652RA	143891	0.01	
6V2652RA	143892	0.01	
6V2652RA	*PGMS-6	1.45	
6V2652RA	*BLANK	<0.01	

1

Certificate Number	Sample Name	Assay Au g/tonne	Assay Au-check g/tonne
6V2748RA	143893	<0.01	<0.01
6V2748RA	143894	<0.01	
6V2748RA	143895	0.01	
6V2748RA	143896	<0.01	
6V2748RA	143897	<0.01	
6V2748RA	143898	<0.01	
6V2748RA	143899	<0.01	
6V2748RA	143900	<0.01	
6V2748RA	143901	<0.01	
6V2748RA	143902	<0.01	<0.01
6V2748RA	143903	0.01	
6V2748RA	143904	<0.01	
6V2748RA	143905	<0.01	
6V2748RA	143906	<0.01	
6V2748RA	143907	<0.01	
6V2748RA	143908	<0.01	
6V2748RA	143909	<0.01	
6V2748RA	143910	<0.01	
6V2748RA	143911	<0.01	
6V2748RA	143912	<0.01	<0.01
6V2748RA	143913	<0.01	
6V2748RA	143914	<0.01	
6V2748RA	143915	<0.01	
6V2748RA	143916	<0.01	
6V2748RA	*STD OxH37	1.28	
6V2748RA	*BLANK	<0.01	

C - 06 - 01

Certificate Number	Sample Name	Ag ppm	Al ppm	As ppm	Ba ppm	Be ppm	Bt ppm	Ce %	Co ppm	Cr ppm	Cu ppm	Fa ppm	Hg ppm	K %	La ppm	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	S %	Sb ppm	Sc ppm	Sr ppm	Th ppm	Ti %	Tn ppm	U ppm	V ppm	W ppm	Zn ppm	Zr ppm
6V2852RJ	143812	0.2	1.78	0.6	180	0.5	3.35	<1	14	80	38	2.83	<1	0.17	10	1.53	548	3	0.09	27	678	10	0.02	6	186	0.01	<10	25	80	<10	57	5		
6V2852RJ	143813	0.2	1.82	0.6	180	0.5	3.11	<1	13	89	11	3.04	<1	0.12	<10	1.52	638	2	0.12	24	663	0.2	0.01	6	87	0.02	<10	24	78	<10	51	5		
6V2852RJ	143814	0.2	1.82	0.6	180	0.5	1.73	<1	20	94	15	3.71	<1	0.04	<10	2.59	702	<2	0.1	40	787	0.2	0.03	12	47	0.23	<10	18	120	<10	53	15		
6V2852RJ	143815	0.2	4.78	0.6	258	0.5	5.88	<1	57	496	50	6.09	<1	0.02	<10	7.8	1082	2	0.09	408	540	0.2	0.08	5	18	0.12	<10	34	111	<10	52	12		
6V2852RJ	143816	0.2	0.85	0.6	205	0.5	8.53	<1	83	879	10	4.12	<1	<0.01	<10	9.01	778	4	0.03	1500	98	2	0.17	8	253	0.01	<10	80	38	<10	22	3		
6V2852RJ	143817	0.2	1.02	0.6	28	0.5	2.89	<1	101	1128	12	3.51	<1	<0.01	<10	9.38	743	3	0.08	1785	101	2	0.18	14	10	0.03	<10	22	36	<10	23	4		
6V2852RJ	143818	0.2	1.79	0.6	19	0.5	3.28	<1	88	1019	18	3.92	<1	<0.01	<10	8.91	777	3	0.1	1438	172	0.2	0.21	11	10	0.07	<10	32	53	<10	32	8		
6V2852RJ	143819	0.2	2	0.6	31	0.5	4.49	<1	92	1144	20	4.1	<1	<0.01	<10	9.04	908	4	0.12	1513	198	0.2	0.24	13	12	0.05	<10	37	80	<10	33	6		
6V2852RJ	143820	0.2	3.49	0.6	144	0.5	3.28	<1	54	708	35	4.74	<1	0.01	<10	8.75	895	3	0.12	783	369	0.2	0.21	8	13	0.05	<10	30	95	<10	82	5		
6V2852RJ	143821	0.2	4.11	10	84	0.8	2.78	<1	47	707	38	4.94	<1	<0.01	<10	8.91	827	5	0.13	654	483	0.2	0.36	7	13	0.04	<10	28	108	<10	81	4		
6V2852RJ	143822	0.2	4.13	0.6	208	0.5	2.01	<1	43	544	48	6.05	<1	0.02	<10	8.5	823	4	0.11	537	538	0.2	0.37	5	14	0.04	<10	20	120	<10	85	4		
6V2852RJ	143823	0.2	2.5	0.6	771	0.5	2.44	<1	15	183	34	3.27	<1	0.04	<10	5.19	868	3	0.07	199	405	0.2	0.18	5	7	0.01	<10	18	57	<10	54	3		
6V2852RJ	143824	0.2	3.35	0.6	291	0.5	1.83	<1	21	252	39	4.29	<1	0.04	<10	6.73	889	2	0.11	278	487	0.2	0.45	11	77	0.04	<10	15	101	<10	71	4		
6V2852RJ	143825	0.2	2.04	0.6	141	0.5	1.4	<1	14	109	45	3.14	<1	0.11	13	3.08	515	4	0.05	95	1418	0.2	0.24	7	42	0.04	<10	18	46	<10	70	4		
6V2852RJ	143826	0.2	2.19	0.6	72	0.5	0.8	<1	18	170	65	3.38	<1	0.12	<10	3.35	548	10	0.05	158	456	0.2	0.34	5	7	0.01	<10	10	57	<10	78	4		
6V2852RJ	143827	0.2	2.48	0.6	801	0.5	1.85	<1	28	222	35	4.18	<1	0.11	<10	3.45	714	2	0.05	252	571	0.2	0.24	7	80	0.04	<10	20	79	<10	88	4		
6V2852RJ	143828	0.2	2.1	0.6	303	0.5	1.15	<1	18	20	32	5.08	<1	0.21	<10	1.38	680	<2	0.07	22	424	2	0.41	17	37	0.04	<10	13	74	<10	104	4		
6V2852RJ	143829	0.2	2.43	0.6	153	0.5	2.73	<1	23	98	42	5.22	<1	0.15	<10	2.32	922	4	0.06	121	719	2	0.54	11	90	0.04	<10	27	85	<10	104	5		
6V2852RJ	143830	0.2	3.62	0.6	9	0.5	3.52	<1	53	403	40	5.87	<1	0.07	<10	5.07	1033	4	0.06	872	864	0.2	0.31	11	70	0.04	<10	36	105	<10	104	5		
6V2852RJ	143831	0.2	2	0.6	878	0.5	2.29	<1	20	156	37	3.79	<1	0.12	<10	2.42	758	3	0.04	148	801	0.2	0.2	8	67	0.04	<10	19	59	<10	74	4		
6V2852RJ	143832	0.2	2.44	0.6	128	0.5	2.87	<1	63	851	38	4.43	<1	0.09	<10	4.8	1128	3	0.07	1098	395	0.2	0.3	7	11	0.07	<10	25	74	<10	79	4		
6V2852RJ	143833	0.2	2.62	0.6	74	0.5	1.88	<1	13	107	24	4.18	<1	0.08	<10	4.61	901	3	0.08	114	820	0.2	0.29	9	107	0.04	<10	14	88	<10	77	4		
6V2852RJ	143834	0.2	1.78	10	72	0.5	0.98	<1	13	70	28	4.02	<1	0.15	<10	1.98	888	<2	0.09	54	655	5	0.43	10	45	0.04	<10	10	53	<10	100	4		
6V2852RJ	143835	0.2	1.89	10	137	0.5	1.31	<1	11	22	23	3.81	<1	0.19	<10	2.04	821	2	0.09	30	515	5	0.41	10	64	0.04	<10	10	44	<10	100	4		
6V2852RJ	143836	0.2	2.1	10	87	0.5	1.39	<1	14	119	29	3.87	<1	0.15	<10	3.11	842	2	0.08	92	584	4	0.49	9	68	0.04	<10	17	54	<10	98	4		
6V2852RJ	143837	0.2	2.32	11	58	0.5	1.48	<1	12	98	28	3.98	<1	0.11	<10	3.72	875	2	0.08	73	672	5	0.41	9	77	0.04	<10	14	57	<10	90	4		
6V2852RJ	143838	0.2	1.28	12	67	0.5	0.61	<1	11	15	34	3.42	<1	0.18	<10	1.22	608	<2	0.1	18	527	8	0.38	9	48	0.04	<10	10	36	<10	100	4		
6V2852RJ	143839	0.2	1.29	12	68	0.5	1.18	<1	11	15	33	3.55	<1	0.26	<10	1.58	882	2	0.09	21	815	8	0.32	8	78	0.04	<10	10	38	<10	91	4		
6V2852RJ	143840	0.2	1.04	33	161	0.5	1.28	<1	10	18	20	3.33	<1	0.27	<10	1.43	611	<2	0.1	18	443	5	0.37	8	78	0.04	<10	15	37	<10	83	4		
6V2852RJ	143841	0.2	1.67	18	153	0.5	3.43	<1	17	70	17	3.74	<1	0.14	<10	2.83	795	4	0.09	42	844	3	0.57	7	104	7	0.04	<10	32	81	<10	82	3	
6V2852RJ	143842	0.2	1.7	33	120	0.5	3.58	<1	21	85	27	4.47	<1	0.18	<10	2.92	948	3	0.09	80	887	0.2	0.52	10	114	7	0.04	<10	34	88	<10	82	4	
6V2852RJ	143843	0.2	0.74	128	50	0.5	4.8	<1	34	108	51	8.41	<1	0.12	<10	3.03	1272	4	0.05	188	598	5	0.77	9	15	0.04	<10	33	85	<10	78	4		
6V2852RJ	143844	0.2	0.77	1348	40	0.5	4.51	10	33	38	45	8.4	<1	0.38	14	2	1038	4	0.07	102	1923	5	2.81	24	12	123	7	0.04	<10	43	49	<10	97	5
6V2852RJ	143845	0.2	1.03	1121	50	0.5	4.87	8	39	59	50	8.52	<1	0.34	<10	2.99	1227	3	0.07	113	1298	5	2.85	20	18	92	8	0.04	<10	40	55	<10	107	6
6V2852RJ	143846	0.2	1.97	7	47	0.5	2.55	<1	44	111	41	7.24	<1	0.15	<10	2.89	1403	2	0.08	114	1219	0.2	0.03	21	92	0.04	<10	16	104	<10	142	10		
6V2852RJ	143847	0.2	1.12	8	53	0.5	3.41	<1	45	74	57	7.18	<1	0.18	<10	2.37	1389	2	0.09	99	1312	5	0.73	18	132	0.04	<10	19	73	<10	143	12		
6V2852RJ	143848	0.2	1.34	104	58	0.6	3.02	<1	51	83	39	8.02	<1	0.18	<10	2.45	1365	2	0.08	118	1508	4	2.08	10	20	115	0.04	<10	25	87	<10	157	12	
6V2852RJ	143849	0.2	0.44	2863	34	0.5	3.88	23	46	22	51	7.58	<1	0.24	<10	1.75	1175	2	0.08	101	1078	8	0.00	37	13	92	0.04	<10	32	29	<10	184	7	
6V2852RJ	143850	0.2	1.14	10	74	0.6	1.3	<1	41	85	73	7.17	<1	0.25	<10	1.55	907	<2	0.09	145	1252	5	0.27	19	101	0.04	<10	16	92	<10	124	13		
6V2852RJ	143851	0.2	0.24	713	36	0.5	8.85	5	43	158	25	4.14	<1	0.08	<10	6.88	818	4	0.02	896	282	3	0.99	181	8	295	5	0.04	<10	41	31	<10	50	3
6V2852RJ	143852	0.2	0.43	5573	53	0.5	5.33	47	30	124	24	3.24	<1	0.13	<10	2.72	872	5	0.04	332	250	5	1.38	149	9	185	5	0.04	<10	37	30	<10	41	3
6V2852RJ	143853	0.2	0.29	2998	50	0.5	8.47	25	29	58	30	3.97	<1	0.13	<10	3.82	783	4	0.05	285	300	5	1.94	81	14	265	5	0.04	<10	41	38	<10	51	3
6V2852RJ	143854	0.2	0.44	3077	62	0.5	5.85	28	30	54	27	4.58	<1	0.17	<10	3.2	958	4	0.07	116	420	14	2.83	61	18	213	5	0.04	<10	41	43	<10	68	4
6V2852RJ	143855	0.2	1.95	18	31	0.5	8.8	<1	39	132	33	5.78	<1	0.07	<10	2.51	984	3	0.13	142														

Certificate Number	Sample Name	ICP Ag ppm	ICP Al %	ICP As ppm	ICP Ba ppm	ICP Be ppm	ICP Bi ppm	ICP Ca %	ICP Cd ppm	ICP Co ppm	ICP Cr ppm	ICP Cu ppm	ICP Fe %	ICP Hg ppm	ICP K %	ICP La ppm	ICP Mg %	ICP Mn ppm	ICP Mo ppm	ICP Na %	ICP Ni ppm	ICP P ppm	ICP Pb ppm	ICP S %	ICP Sb ppm	ICP Sc ppm	ICP Sr ppm	ICP Th ppm	ICP Ti %	ICP Tl ppm	ICP U ppm	ICP V ppm	ICP W ppm	ICP Zn ppm	ICP Zr ppm
8V2748RJ	143893	<0.2	3.17		56	0.9		3.78	<1	48	117	81	7.69	2	0.11	12	1.87	1467	<2	0.11	100	1810	9	0.03	<5	21	88		0.11	10	<10	96	<10	198	15
8V2748RJ	143894	<0.2	2.41	<5	31	0.8	<5	5.44	3	41	118	73	6.91	1	0.14	12	2.47	1570	<2	0.13	89	1455	199	0.06	<5	20	151		0.01	<10	<10	122	<10	515	7
8V2748RJ	143895	<0.2	3.13	<5	54	0.7	<5	3.72	<1	46	118	51	7.49	<1	0.18	13	2.05	1825	<2	0.09	101	1358	9	0.03	<5	18	89		0.01	<10	<10	108	<10	158	7
8V2748RJ	143896	<0.2	2.35	<5	34	0.8	<5	10.08	<1	38	109	39	5.35	1	0.09	<10	1.86	1546	<2	0.1	92	1119	<2	0.07	<5	17	173		0.46	10	<10	149	<10	55	22
8V2748RJ	143897	<0.2	1.86	<5	97	0.5	<5	7.89	<1	22	54	125	10.42	<1	0.07	32	1.38	4800	<2	0.02	144	1668	35	0.04	6	8	120		0.05	<10	<10	238	<10	81	19
8V2748RJ	143898	<0.2	3.1	<5	29	0.9	<5	7.35	<1	41	125	45	6.14	2	0.11	11	2.78	2003	<2	0.1	100	1462	5	0.09	<5	19	122		0.35	10	<10	198	<10	87	16
8V2748RJ	143899	<0.2	3.97	<5	25	0.7	<5	5.02	<1	45	135	57	8.08	<1	0.07	<10	4.85	1111	<2	0.16	183	1065	<2	0.08	<5	14	104		0.39	<10	<10	151	<10	86	22
8V2748RJ	143900	<0.2	3.85	<5	17	0.6	<5	3.35	<1	58	479	50	5.55	<1	0.03	<10	6.37	745	<2	0.2	356	909	<2	<0.01	8	9	79		0.41	<10	<10	117	<10	83	36
8V2748RJ	143901	<0.2	4.04	<5	17	<0.5	<5	2.17	<1	79	1074	41	6.7	<1	0.01	<10	10.28	888	<2	0.28	704	712	<2	0.04	17	6	104		0.21	<10	<10	88	<10	73	18
8V2748RJ	143902	<0.2	2.11	<5	63	<0.5	<5	6.71	<1	40	234	43	5.27	<1	0.1	<10	5.11	1085	<2	0.21	273	664	<2	0.09	<5	14	224		0.03	<10	<10	89	<10	55	14
8V2748RJ	143903	<0.2	2	<5	187	0.5	<5	7.08	<1	33	155	44	5.35	<1	0.04	<10	4.05	960	<2	0.12	143	815	6	0.13	<5	17	169		0.21	<10	<10	138	<10	56	31
8V2748RJ	143904	<0.2	3.32	<5	41	0.8	<5	4.11	<1	38	96	59	5.87	<1	0.1	<10	3.22	784	<2	0.15	104	1100	4	0.05	<5	13	97		0.41	<10	<10	133	<10	71	34
8V2748RJ	143905	<0.2	4.05	<5	27	0.9	<5	4.07	<1	45	181	80	6.33	<1	0.04	<10	4.63	1156	<2	0.17	128	1156	6	0.12	<5	21	99		0.51	<10	<10	200	<10	75	59
8V2748RJ	143906	<0.2	4.41	<5	16	0.8	<5	3.88	<1	54	384	54	8.02	<1	0.05	<10	5.57	839	<2	0.17	302	985	<2	0.07	<5	11	92		0.51	<10	<10	134	<10	71	32
8V2748RJ	143907	<0.2	4.8	<5	20	0.8	<5	3.37	<1	55	522	49	6.54	<1	0.03	<10	9.24	900	<2	0.27	400	872	<2	0.09	<5	11	129		0.44	<10	<10	125	<10	67	27
8V2748RJ	143908	<0.2	4.81	<5	20	0.5	<5	3.16	<1	76	893	42	6.52	<1	0.02	<10	9.72	876	<2	0.31	610	748	<2	0.04	9	5	148		0.38	<10	<10	96	<10	64	22
8V2748RJ	143909	<0.2	4.87	<5	21	0.6	<5	4.19	<1	58	480	45	8.04	<1	0.02	<10	7.89	870	<2	0.24	407	847	<2	0.07	<5	7	135		0.43	<10	<10	108	<10	63	25
8V2748RJ	143910	<0.2	3.91	<5	21	0.9	<5	3.78	<1	43	132	80	5.88	<1	0.06	<10	4.08	968	<2	0.15	118	1058	5	0.12	<5	13	80		0.64	19	<10	158	<10	71	41
8V2748RJ	143911	<0.2	3.72	<5	18	0.6	<5	5.86	<1	38	150	55	6.38	<1	0.12	<10	4.86	1287	<2	0.13	132	963	3	0.06	<5	18	150		0.2	20	<10	198	<10	89	12
8V2748RJ	143912	0.2	3.42	<5	20	0.8	<5	3.34	<1	43	124	56	5.76	<1	0.04	<10	4.13	965	<2	0.19	139	1053	8	0.09	<5	12	96		0.55	29	<10	150	<10	69	39
8V2748RJ	143913	0.9	3.55	7	25	0.6	<5	9.58	<1	52	373	45	6.21	<1	0.14	<10	4.15	1270	<2	0.09	331	894	<2	0.37	<5	18	215		0.01	10	<10	120	<10	66	8
8V2748RJ	143914	1.2	2.27	<5	16	0.8	<5	5.5	<1	77	174	85	3.62	<1	0.09	10	2.18	800	<2	0.14	188	1384	6	0.11	7	20	89		0.71	18	<10	198	<10	48	15
8V2748RJ	143915	0.8	4.6	<5	27	1.7	<5	7.43	<1	56	160	48	6.78	<1	0.14	10	3.27	1337	<2	0.1	128	1591	8	0.02	<5	24	126		1.04	37	<10	234	<10	86	99
8V2748RJ	143916	0.7	4.23	<5	22	1.2	<5	7.03	<1	47	157	48	8.04	<1	0.1	10	2.9	1008	<2	0.1	108	1363	5	0.13	<5	19	156		0.6	14	<10	178	<10	76	59
8V2748RJ	143917	<0.2	3.61	<5	18	0.7	<5	5.83	<1	37	168	56	5.43	<1	0.08	<10	3.47	957	<2	0.1	97	1000	<2	0.09	<5	19	120		0.23	26	<10	138	<10	62	24
8V2748RJ	143918	<0.2	2.8	<5	35	1.1	<5	5.43	<1	51	184	53	6.18	<1	0.05	11	3.61	1025	<2	0.08	172	1359	10	<0.01	13	25	168		0.42	19	<10	201	<10	77	26
8V2748RJ	143919	<0.2	2.27	<5	26	0.7	<5	11.59	<1	43	105	45	5.18	<1	0.14	10	2.2	2191	2	0.08	144	1084	7	0.26	<5	14	147		0.29	21	<10	130	<10	52	14
8V2748RJ	143920	<0.2	2.18	<5	33	0.7	<5	14.54	<1	42	114	36	5.38	<1	0.11	<10	1.79	1509	2	0.11	89	1076	9	0.05	<5	18	192		0.51	39	<10	161	<10	57	25
8V2748RJ	143921	<0.2	2.45	<5	39	0.5	<5	10.76	<1	33	95	52	5.7	1	0.22	17	1.82	4845	<2	0.06	174	1140	3	0.05	<5	15	139		0.03	18	<10	149	<10	72	7
8V2748RJ	143922	<0.2	2.41	<5	21	<0.5	<5	11.8	<1	33	177	61	5.86	<1	0.12	11	1.97	3110	<2	0.06	159	938	12	0.03	<5	15	212		0.01	13	<10	142	<10	62	5
8V2748RJ	143923	<0.2	2.44	<5	20	<0.5	<5	12.11	<1	33	181	61	6.01	<1	0.13	11	1.99	3173	2	0.06	161	953	17	0.08	<5	15	215		0.01	24	<10	145	<10	63	5
8V2748RJ	143924	<0.2	2.34	<5	36	<0.5	<5	11.29	<1	29	88	36	5.29	<1	0.2	10	1.48	1958	4	0.17	77	1224	6	0.31	<5	14	202		0.03	28	<10	116	<10	57	6
8V2748RJ	143925	<0.2	3.01	<5	32	0.5	<5	10.02	<1	37	157	72	7.05	<1	0.12	17	2.77	4728	<2	0.17	218	1514	28	0.09	<5	17	204		0.05	<10	<10	161	<10	78	10
8V2748RJ	143926	<0.2	3.28	<5	38	0.7	<5	7.81	<1	44	167	88	5.85	<1	0.09	<10	4.73	2277	<2	0.16	195	1054	10	0.09	<5	20	205		0.2	19	<10	160	<10	83	13
8V2748RJ	143927	<0.2	2.09	<5	22	0.5	<5	9.12	<1	36	144	50	5.75	<1	0.1	10	2.42	2229	<2	0.08	110	1055	10	0.03	<5	15	173		0.05	17	<10	130	<10	68	7
8V2748RJ	143928	<0.2	1.75	<5	19	0.6	<5	9.89	<1	40	150	52	5.23	<1	0.07	<10	3.2	2718	<2	0.11	138	1072	3	0.01	6	20	172		0.04	21	<10	151	<10	69	7
8V2748RJ	143929	0.4	1	<5	37	0.8	<5	9.5	<1	31	155	20	5.73	<1	0.15	<10	3.52	2588	<2	0.1	112	986	12	<0.01	5	25	197		0.01	22	<10	158	<10	54	7
8V2748RJ	143930	<0.2	4.57	<5	18	<0.5	<5	2.41	<1	82	898	42	6.44	<1	0.02	<10	10.73	862	<2	0.27	898	699	2	<0.01	18	6	112		0.17	25	<10	75	<10	70	13
8V2748RJ	143931	<0.2	4.57	<5	24	<0.5	<5	1.53	<1	79	941	45	6.41	<1	0.01	<10	11.25	758	<2	0.3	711	851	<2	<0.01	20	4	112		0.13	38	<10	69	<10	74	12
8V2748RJ	143932	<0.2	4.78	<5	15	<0.5	<5	2.24	<1	82	884	44	8.55	<1	0.02	<10	11.28	879	<2	0.28	690	873	<2	0.02	11	5	114		0.17	34	<10	75	<10		



**Appendix D**


**Author's Statement of Qualifications**

**Certificate**

I, Christopher J. Sampson, of 2696 West 11<sup>th</sup> Avenue, Vancouver, BC, V6K 2L6 hereby certify that:


1. I am a graduate (1966) of the Royal School of Mines, London University, England with a Bachelor of Science degree (Honours) in Economic Geology.
2. I have practiced my profession of mining exploration for the past 40 years in Canada, Europe, United States, Central and South America. For the past 31 years I have been based in British Columbia.
3. I am a consulting geologist. I am a registered member in good standing of the Association of Professional Engineers of British Columbia.
4. This report is based on supervision of trenching and drilling programmes at the Congress Property, BC, in 2006.

Dated at Vancouver, British Columbia this 5<sup>th</sup> day of May, 2007.



---

Christopher J. Sampson, P.Eng.  
Consulting Geologist

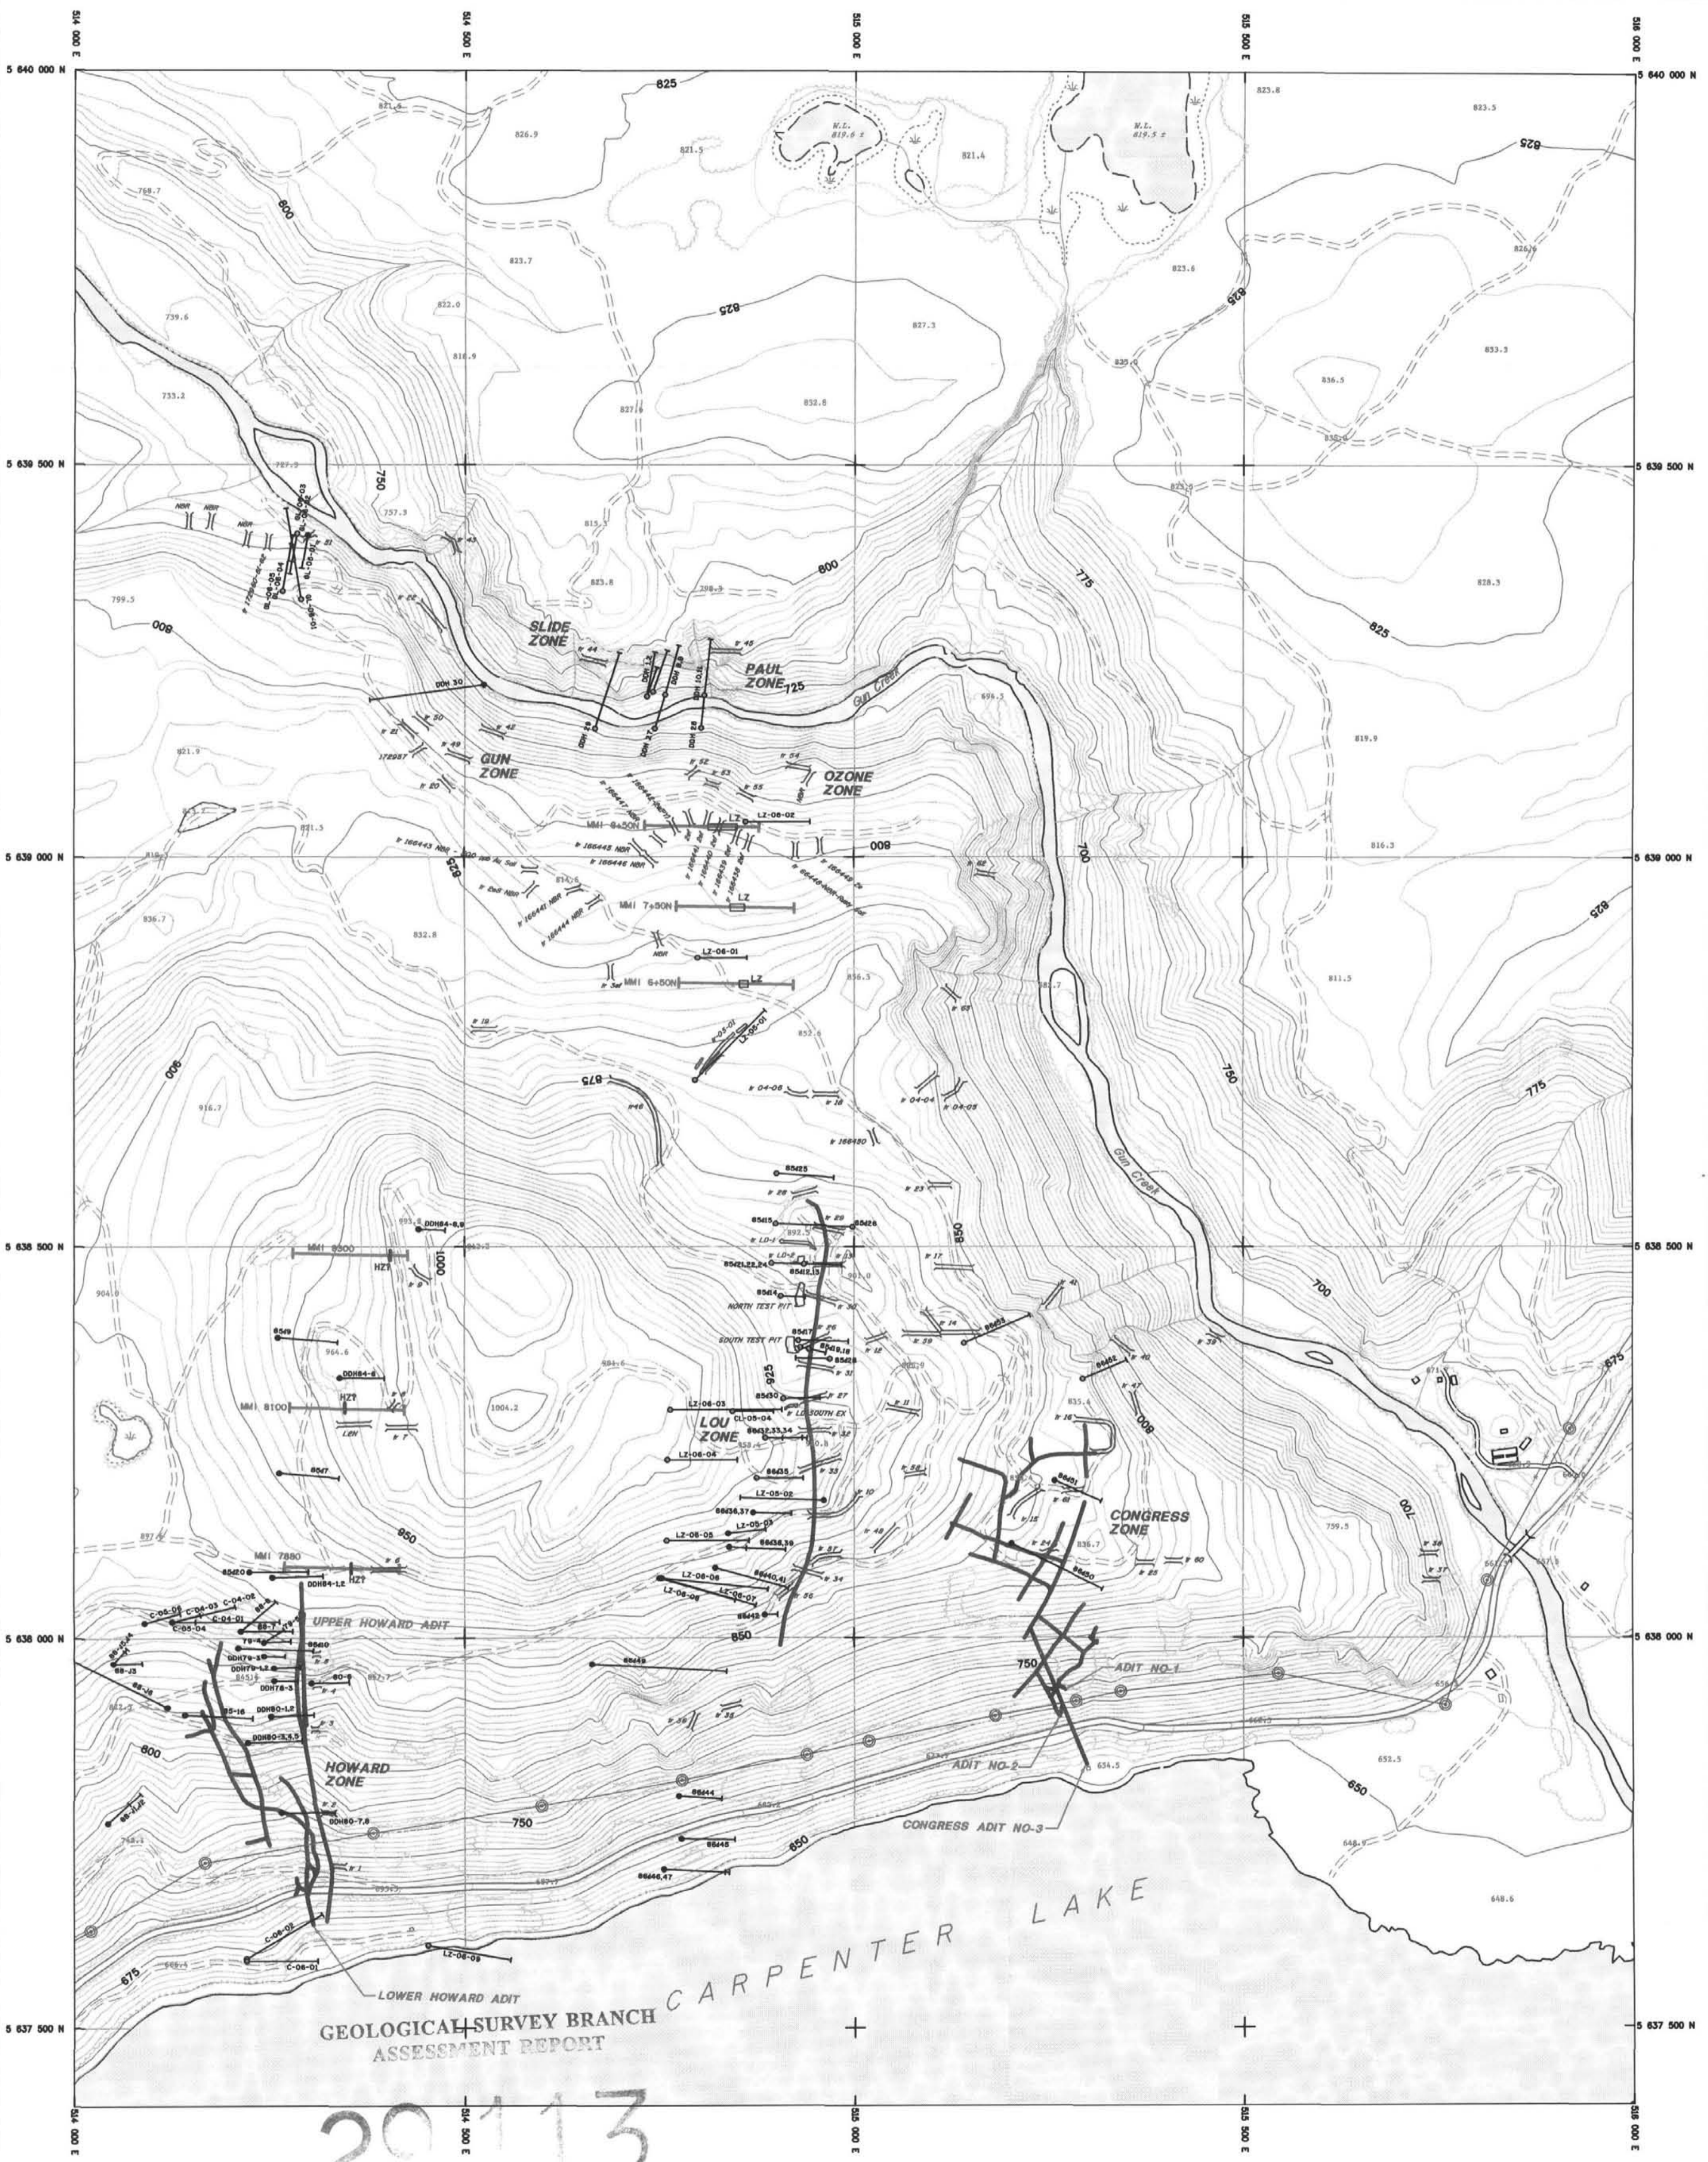

GEOLOGICAL SURVEY BRANCH  
ASSESSMENT REPORT

CARPENTER LAKE

20113



**CONGRESS PROPERTY**  
**GOLDBRIDGE, BC**  
**TRENCHING & DRILLING PROGRAMS**  
**GOLDEN LEDGE - LOU ZONE - HOWARD ZONE**  
**OVERVIEW MAP: 1978 - 2006**

**LEGEND**

Drill Hole Location	Main Road	Swamp
Trench	Road	Wetland
Adit	Trail	Treeline
MMI Sampling	Lake / River	Building
Major Contour	Creek	Spot Height
Minor Contour	Powerline	


Map Base - TRIM - 1:20000  
UTM Zone 10, NAD 83  
BCGS Mapsheet 92J.087 & 097  
NTS Mapsheet: 92J/15  
Contour Interval 5 meters  
Contours Produced by Eagle Mapping Ltd.  
- Source: 2004 Aerial Photography  
File: CONGRESS\_18x24\_5k\_2007-03-23

Prepared By:  
SRS  
www.spatialresource.com  
Tel: 250-828-7165

Map Scale: 1:5000 Date: March 23, 2007

0 50 100 150 200 250 metres

**CONGRESS PROPERTY - HOWARD ZONE**  
**DDH SECTION C-06-01**  
**LOOKING NORTH**

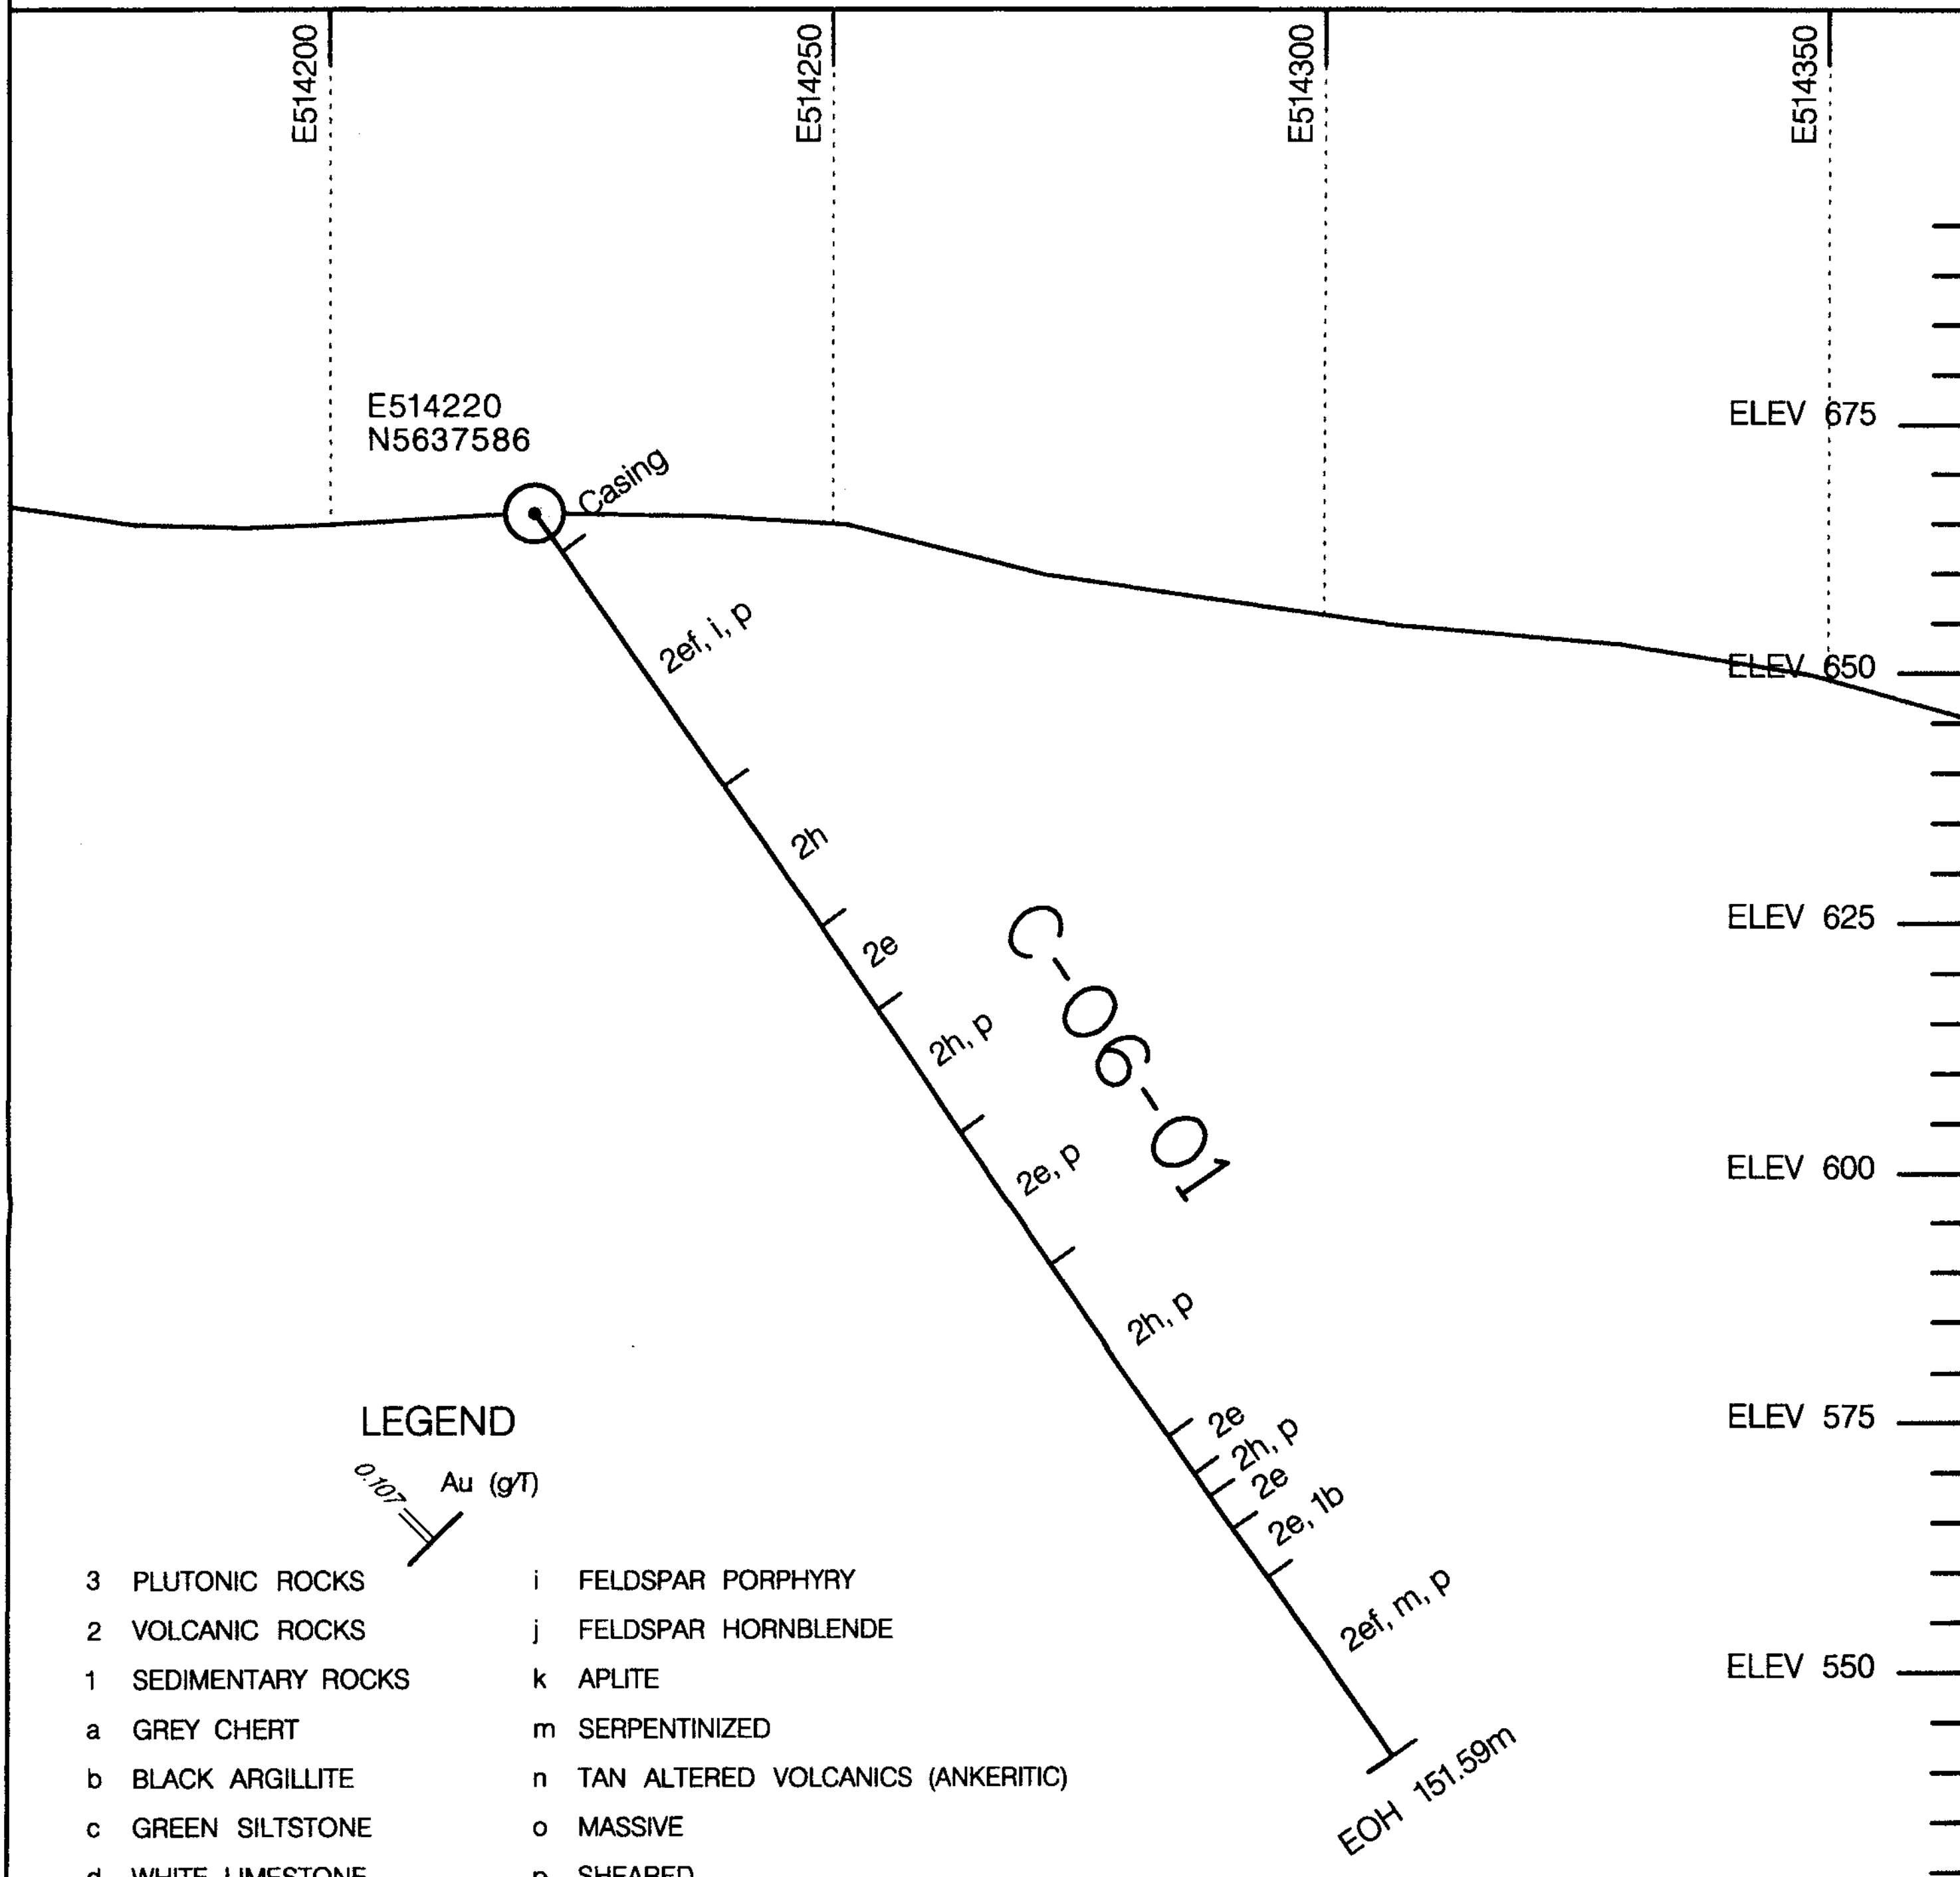

**LEGEND**

0.107 Au (g/T)

- |                     |                                     |
|---------------------|-------------------------------------|
| 3 PLUTONIC ROCKS    | i FELDSPAR PORPHYRY                 |
| 2 VOLCANIC ROCKS    | j FELDSPAR HORNBLLENDE              |
| 1 SEDIMENTARY ROCKS | k APLITE                            |
| a GREY CHERT        | m SERPENTINIZED                     |
| b BLACK ARGILLITE   | n TAN ALTERED VOLCANICS (ANKERITIC) |
| c GREEN SILTSTONE   | o MASSIVE                           |
| d WHITE LIMESTONE   | p SHEARED                           |
| e GREEN BASALT      | q BEDDED                            |
| f PURPLE BASALT     | r JOINTED                           |
| g GREEN TUFF        | s PILLOWED                          |
| h GREEN GABBRO      | t AMYGDALOIDAL                      |


HOLE	AZIMUTH	DIP	EASTING	NORTHING	ELEVATION	LENGTH
C-06-01	90	-55	E514220	N5637586	667	151.59

Scale: 1:1000 Date: May 18, 2007

BCGS Mapsheet: 92J.087, NTS Mapsheet: 92J/15

File: CONGRESS\_C-06-01\_DDH-Section\_8x11\_1k\_2007-05-18

**CONGRESS PROPERTY - HOWARD ZONE**  
**DDH SECTION C-06-02**  
**LOOKING NORTH (60 Degrees)**

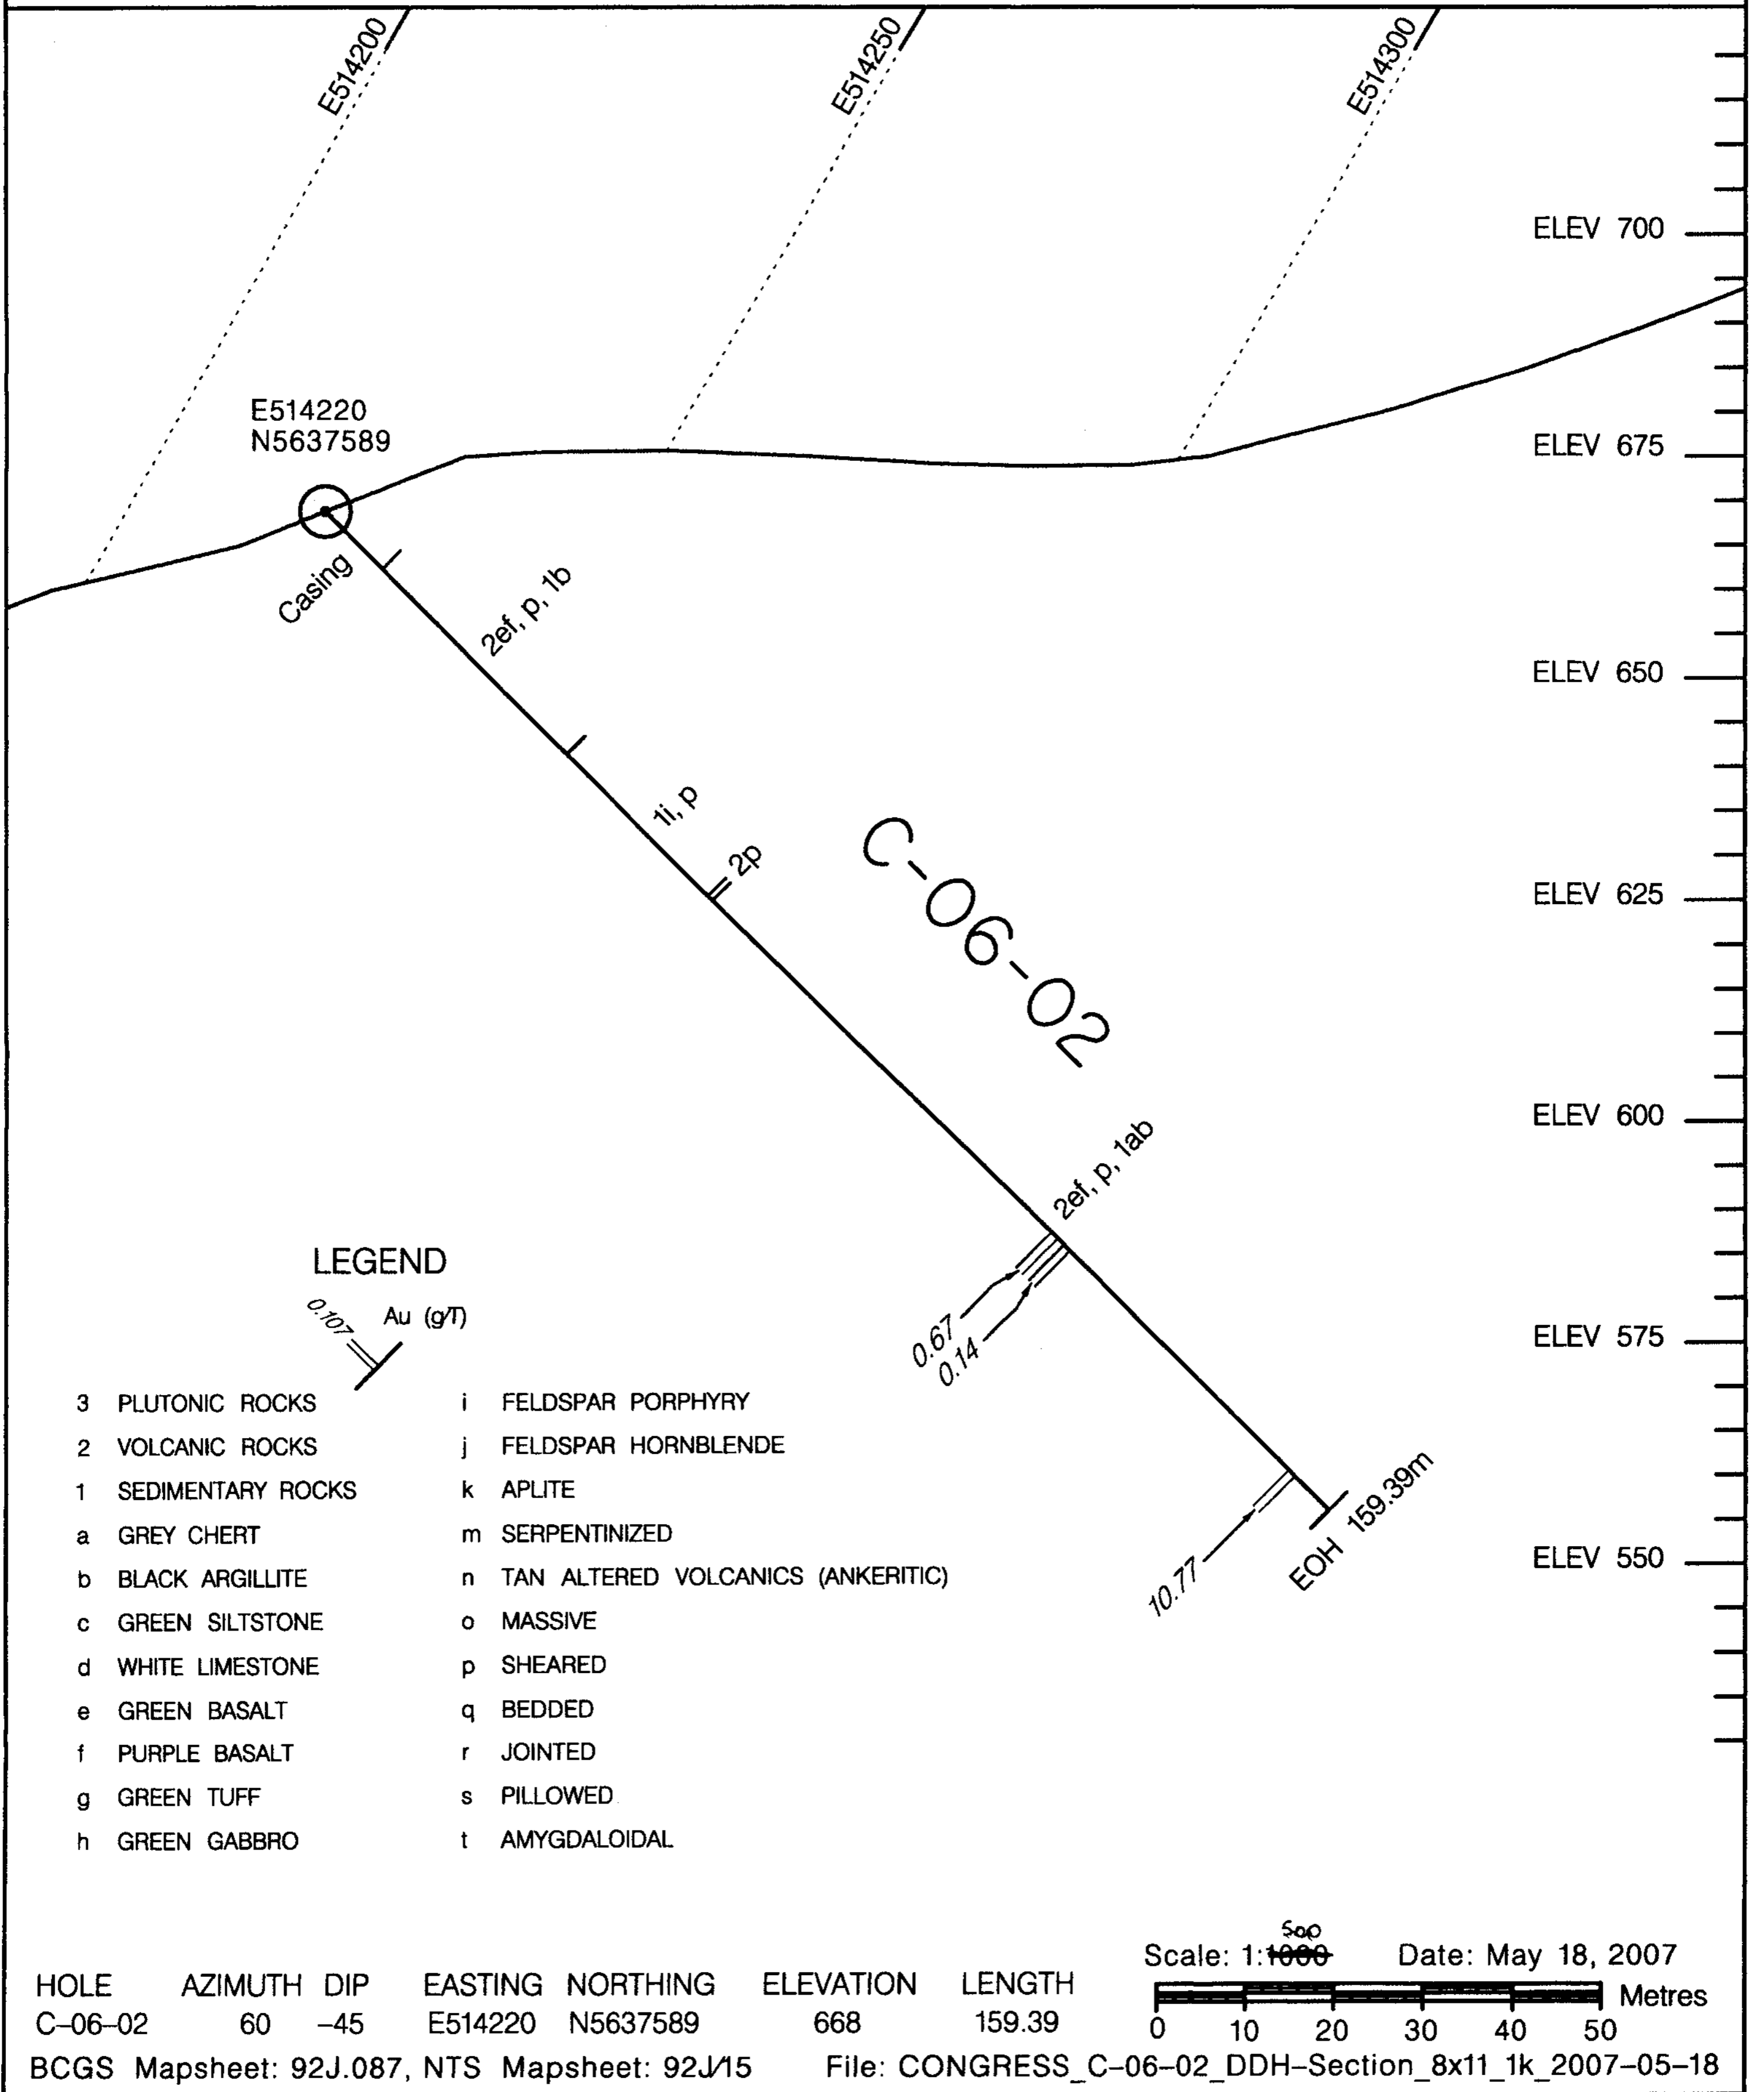

**LEGEND**

0.107 Au (g/T)

- |                     |                                     |
|---------------------|-------------------------------------|
| 3 PLUTONIC ROCKS    | i FELDSPAR PORPHYRY                 |
| 2 VOLCANIC ROCKS    | j FELDSPAR HORNBLLENDE              |
| 1 SEDIMENTARY ROCKS | k APLITE                            |
| a GREY CHERT        | m SERPENTINIZED                     |
| b BLACK ARGILLITE   | n TAN ALTERED VOLCANICS (ANKERITIC) |
| c GREEN SILTSTONE   | o MASSIVE                           |
| d WHITE LIMESTONE   | p SHEARED                           |
| e GREEN BASALT      | q BEDDED                            |
| f PURPLE BASALT     | r JOINTED                           |
| g GREEN TUFF        | s PILLOWED                          |
| h GREEN GABBRO      | t AMYGDALOIDAL                      |

HOLE	AZIMUTH	DIP	EASTING	NORTHING	ELEVATION	LENGTH
C-06-02	60	-45	E514220	N5637589	668	159.39


Scale: 1:1000 Date: May 18, 2007

0 10 20 30 40 50 Metres

BCGS Mapsheet: 92J.087, NTS Mapsheet: 92J/15 File: CONGRESS\_C-06-02\_DDH-Section\_8x11\_1k\_2007-05-18



**CONGRESS PROPERTY - GOLDEN LEDGE**  
**DDH SECTION GL-06-02/03**  
**LOOKING EAST (100 Degrees)**

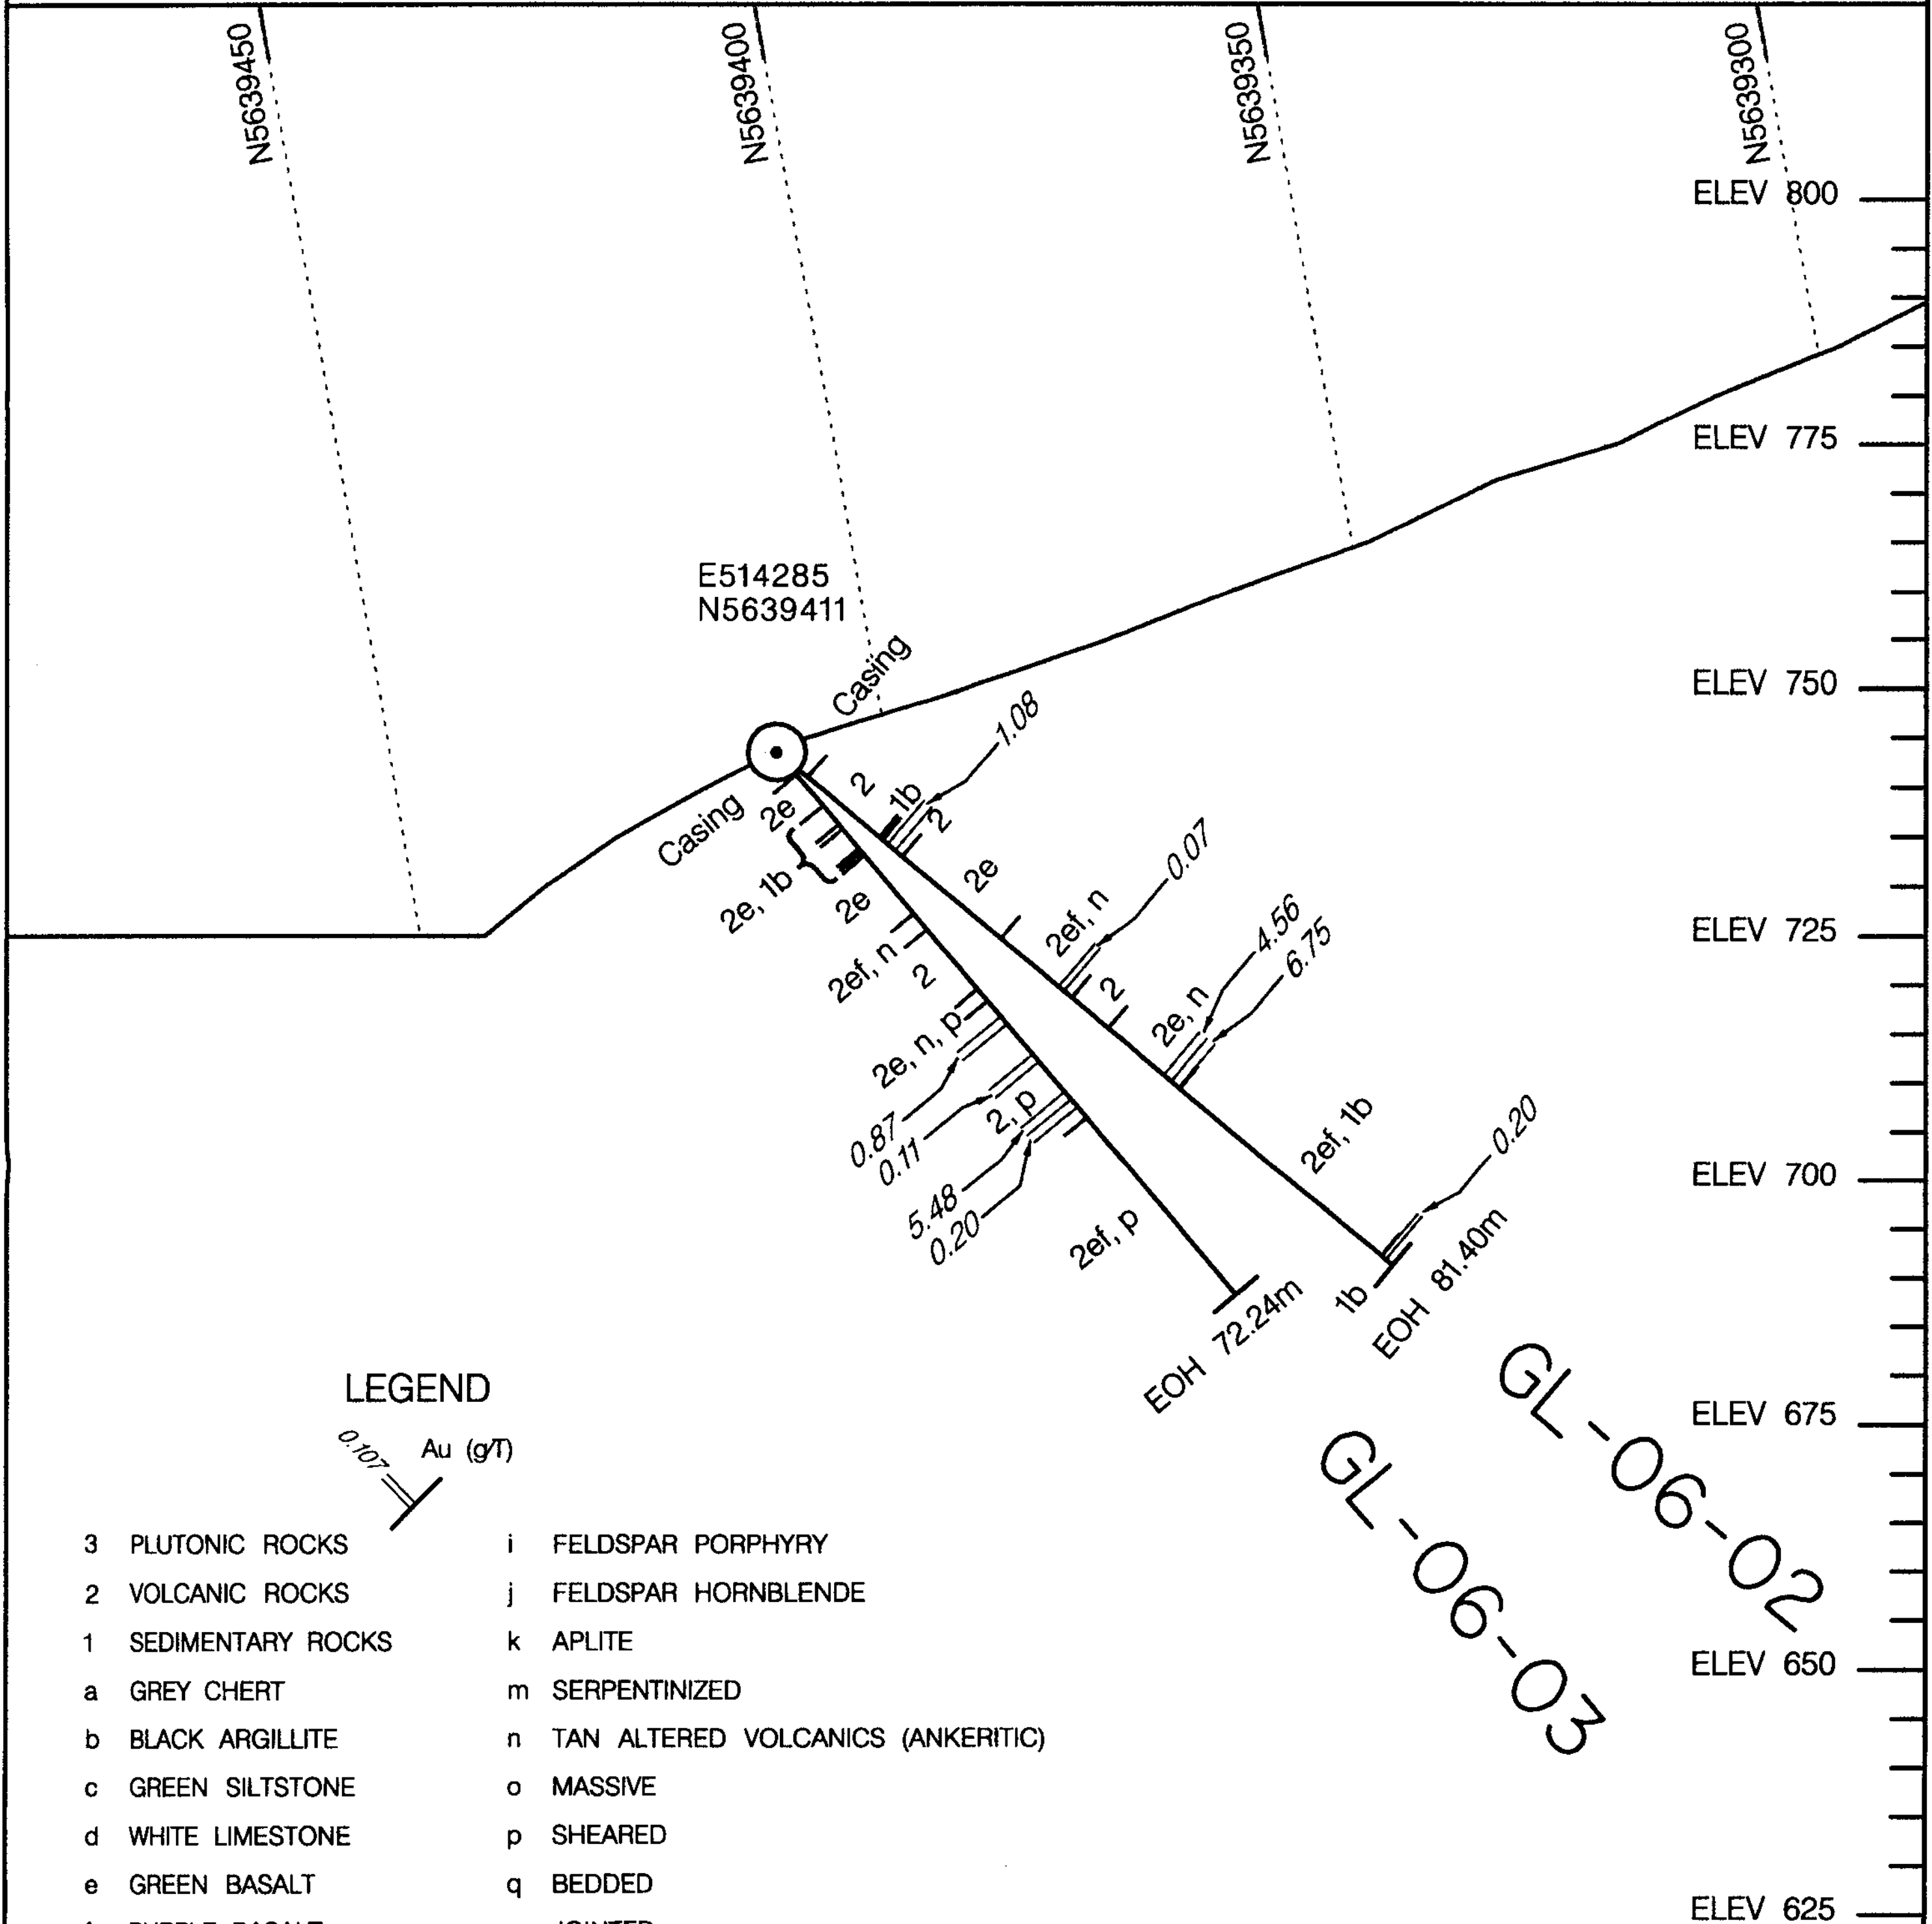

**LEGEND**


0.107 Au (gT)

- |                     |                                     |
|---------------------|-------------------------------------|
| 3 PLUTONIC ROCKS    | i FELDSPAR PORPHYRY                 |
| 2 VOLCANIC ROCKS    | j FELDSPAR HORNBLLENDE              |
| 1 SEDIMENTARY ROCKS | k APLITE                            |
| a GREY CHERT        | m SERPENTINIZED                     |
| b BLACK ARGILLITE   | n TAN ALTERED VOLCANICS (ANKERITIC) |
| c GREEN SILTSTONE   | o MASSIVE                           |
| d WHITE LIMESTONE   | p SHEARED                           |
| e GREEN BASALT      | q BEDDED                            |
| f PURPLE BASALT     | r JOINTED                           |
| g GREEN TUFF        | s PILLOWED                          |
| h GREEN GABBRO      | t AMYGDALOIDAL                      |

HOLE	AZIMUTH	DIP	EASTING	NORTHING	ELEVATION	LENGTH
GL-06-02	190	-50	E514285	N5639411	744	81.40
GL-06-03	190	-60	E514285	N5639411	744	72.24


Scale: 1:1000 Date: May 18 2007

**CONGRESS PROPERTY - GOLDEN LEDGE**  
**DDH SECTION GL-06-04/05**  
**LOOKING EAST (100 Degrees)**

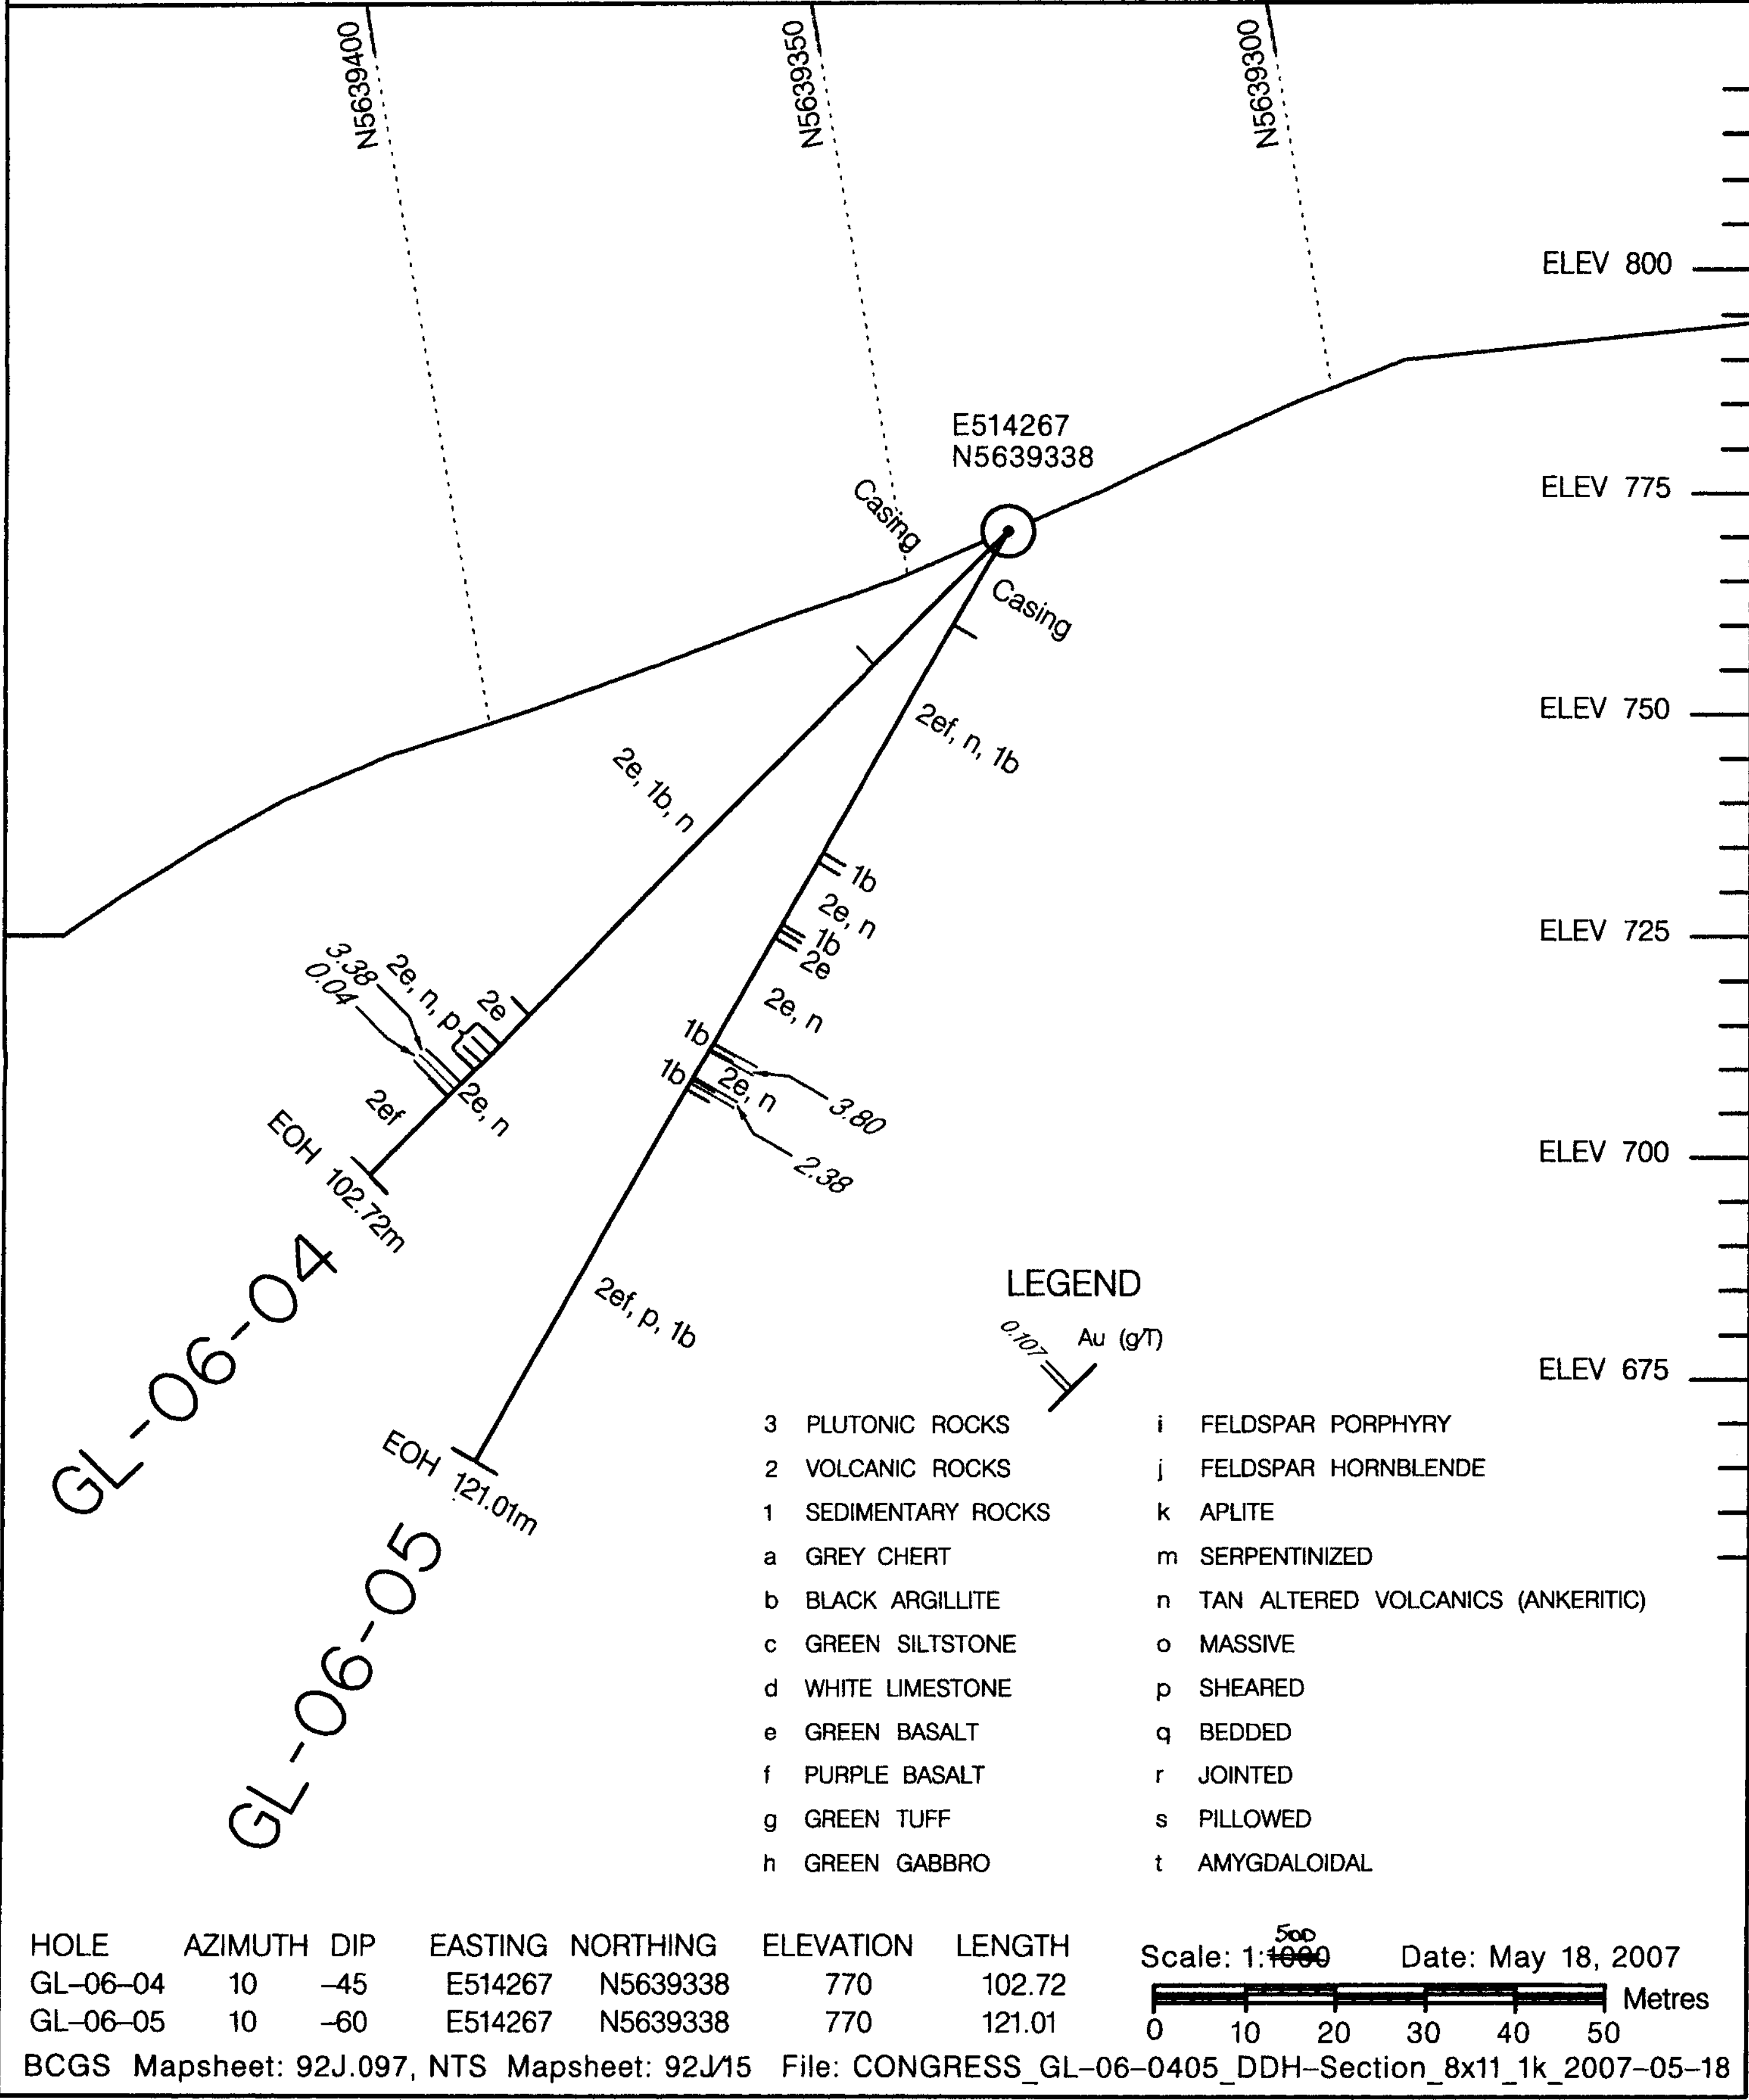



**CONGRESS PROPERTY - LOU ZONE**  
**DDH SECTION LZ-06-01**  
**LOOKING NORTH**

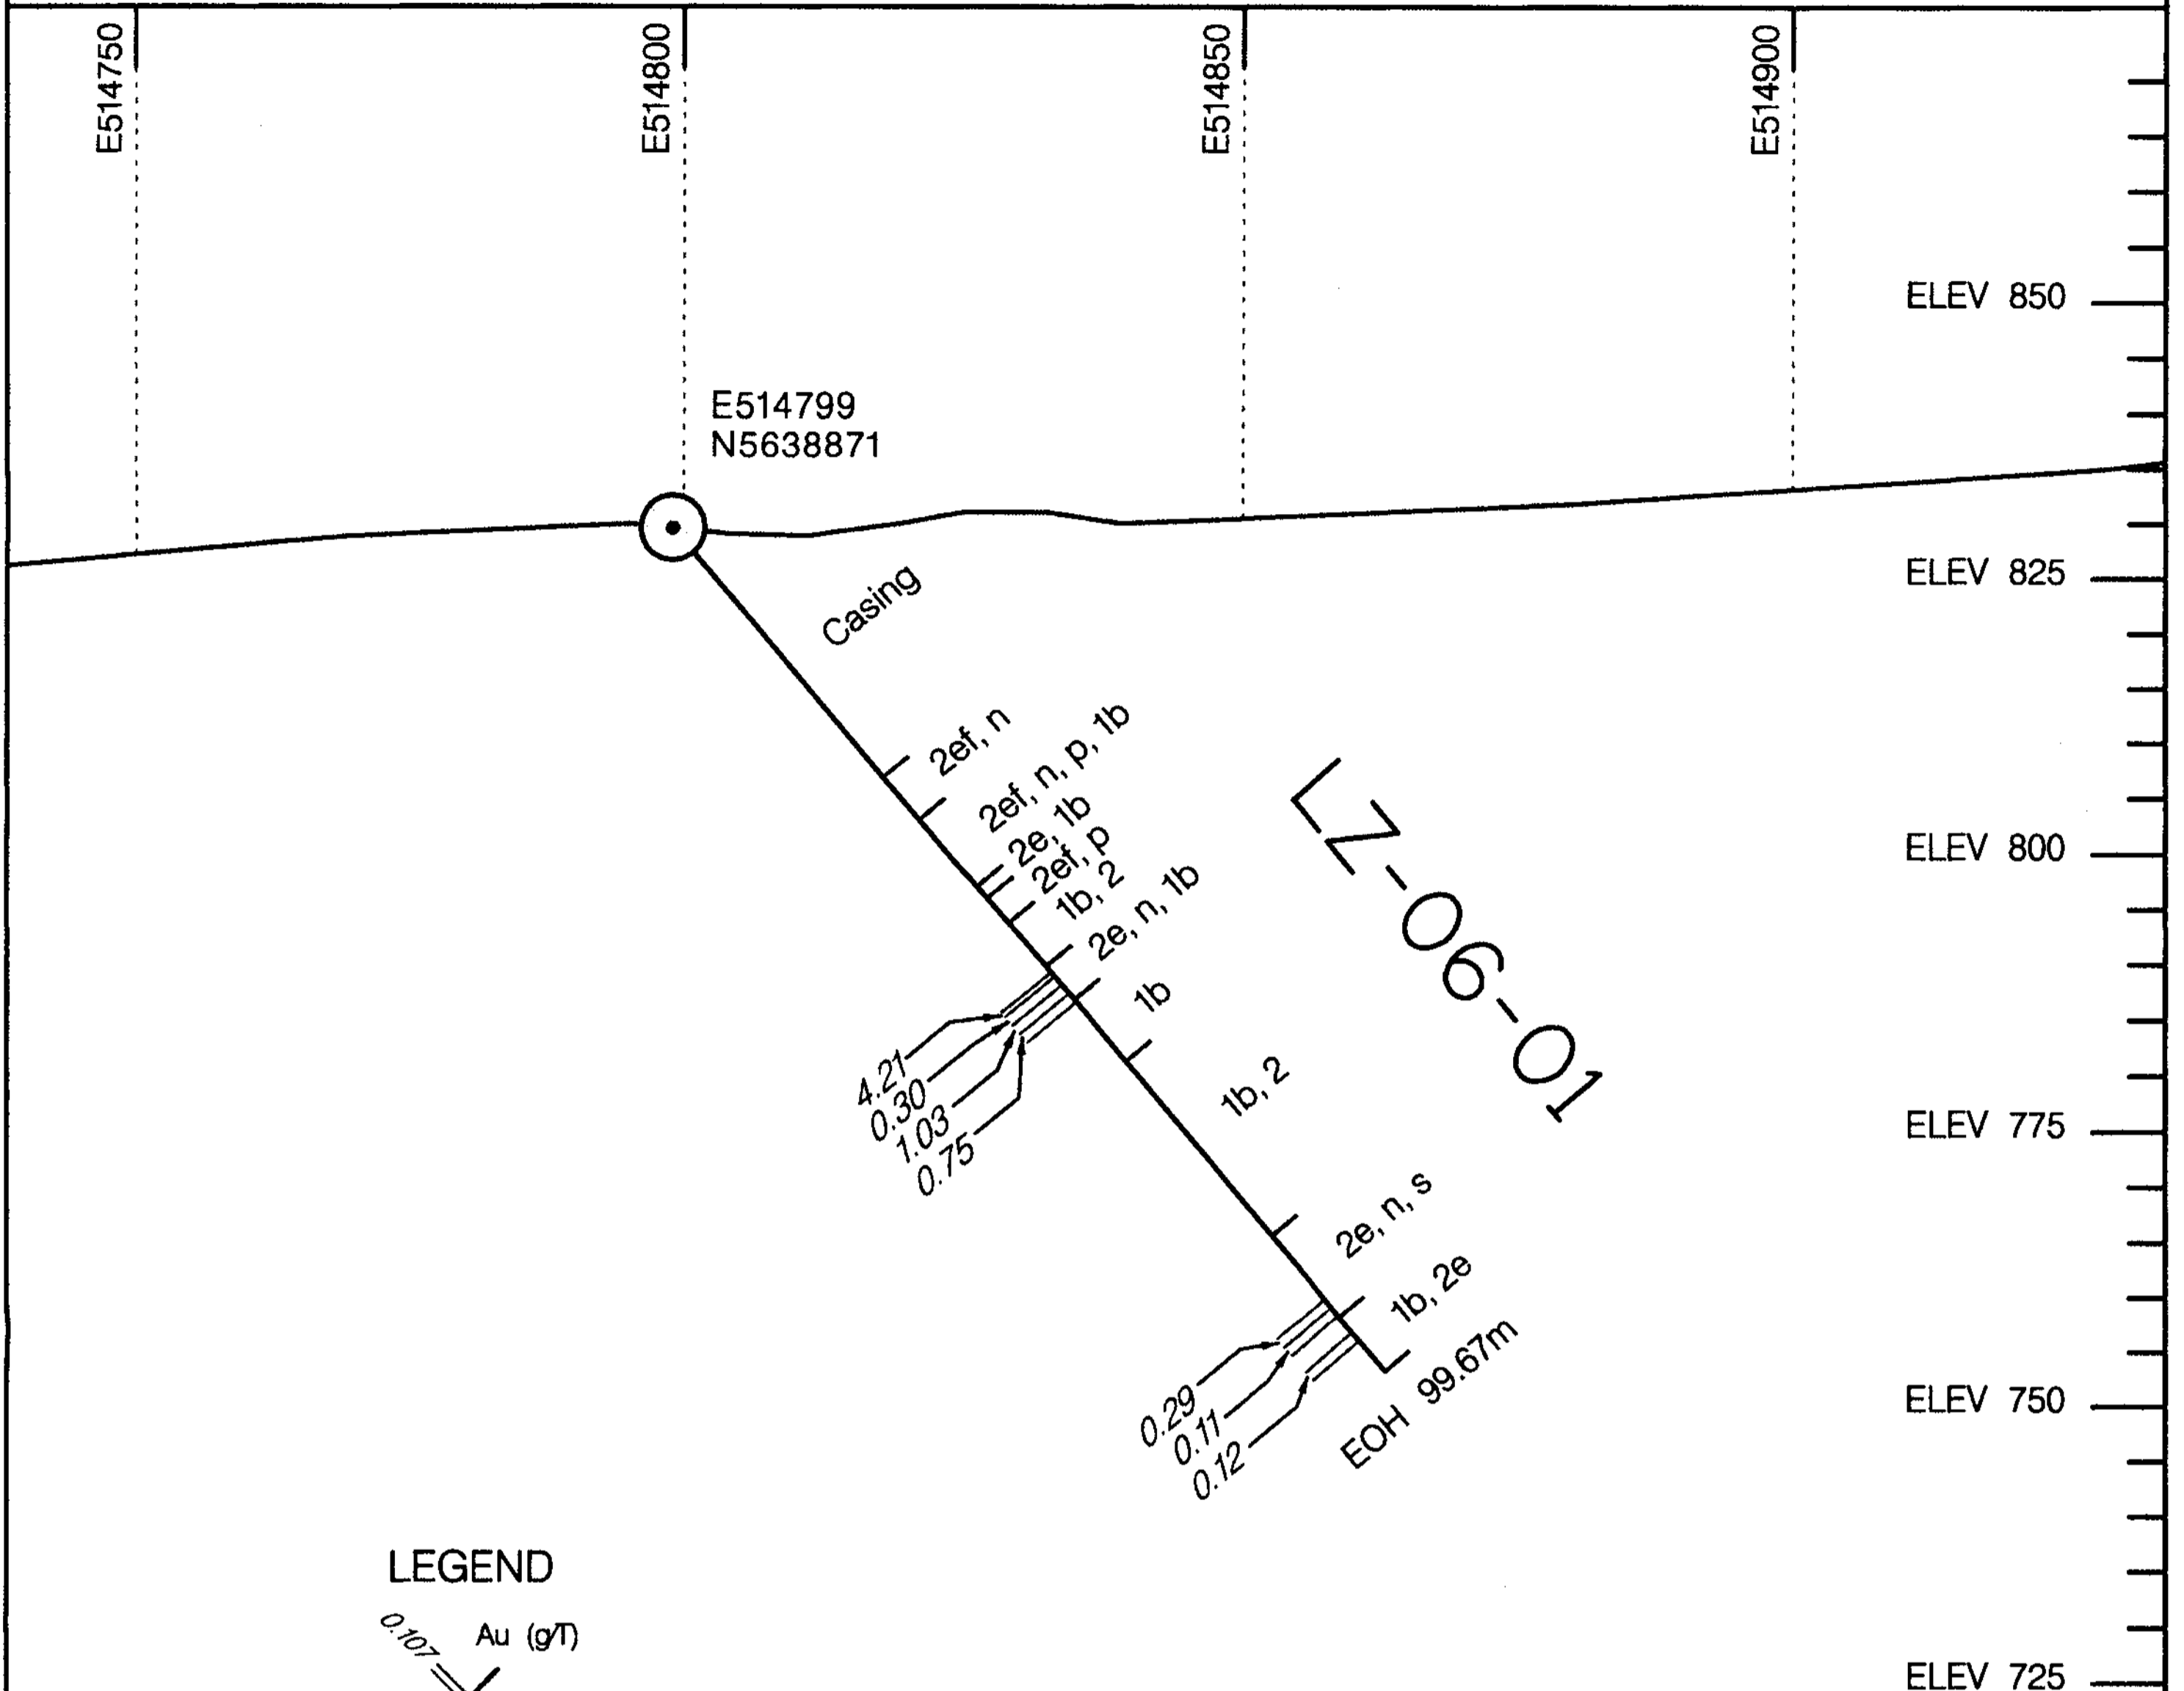

**LEGEND**


0.107 Au (gT)

- |                     |                                     |
|---------------------|-------------------------------------|
| 3 PLUTONIC ROCKS    | i FELDSPAR PORPHYRY                 |
| 2 VOLCANIC ROCKS    | j FELDSPAR HORNBLLENDE              |
| 1 SEDIMENTARY ROCKS | k APLITE                            |
| a GREY CHERT        | m SERPENTINIZED                     |
| b BLACK ARGILLITE   | n TAN ALTERED VOLCANICS (ANKERITIC) |
| c GREEN SILTSTONE   | o MASSIVE                           |
| d WHITE LIMESTONE   | p SHEARED                           |
| e GREEN BASALT      | q BEDDED                            |
| f PURPLE BASALT     | r JOINTED                           |
| g GREEN TUFF        | s PILLOWED                          |
| h GREEN GABBRO      | t AMYGDALOIDAL                      |

HOLE	AZIMUTH	DIP	EASTING	NORTHING	ELEVATION	LENGTH
LZ-06-01	90	-50	E514799	N5638871	837	99.67

Scale: 1:500  
Date: May 18, 2007  
0 10 20 30 40 50 Metres

**CONGRESS PROPERTY - LOU ZONE**  
**DDH SECTION LZ-06-02**  
**LOOKING NORTH**

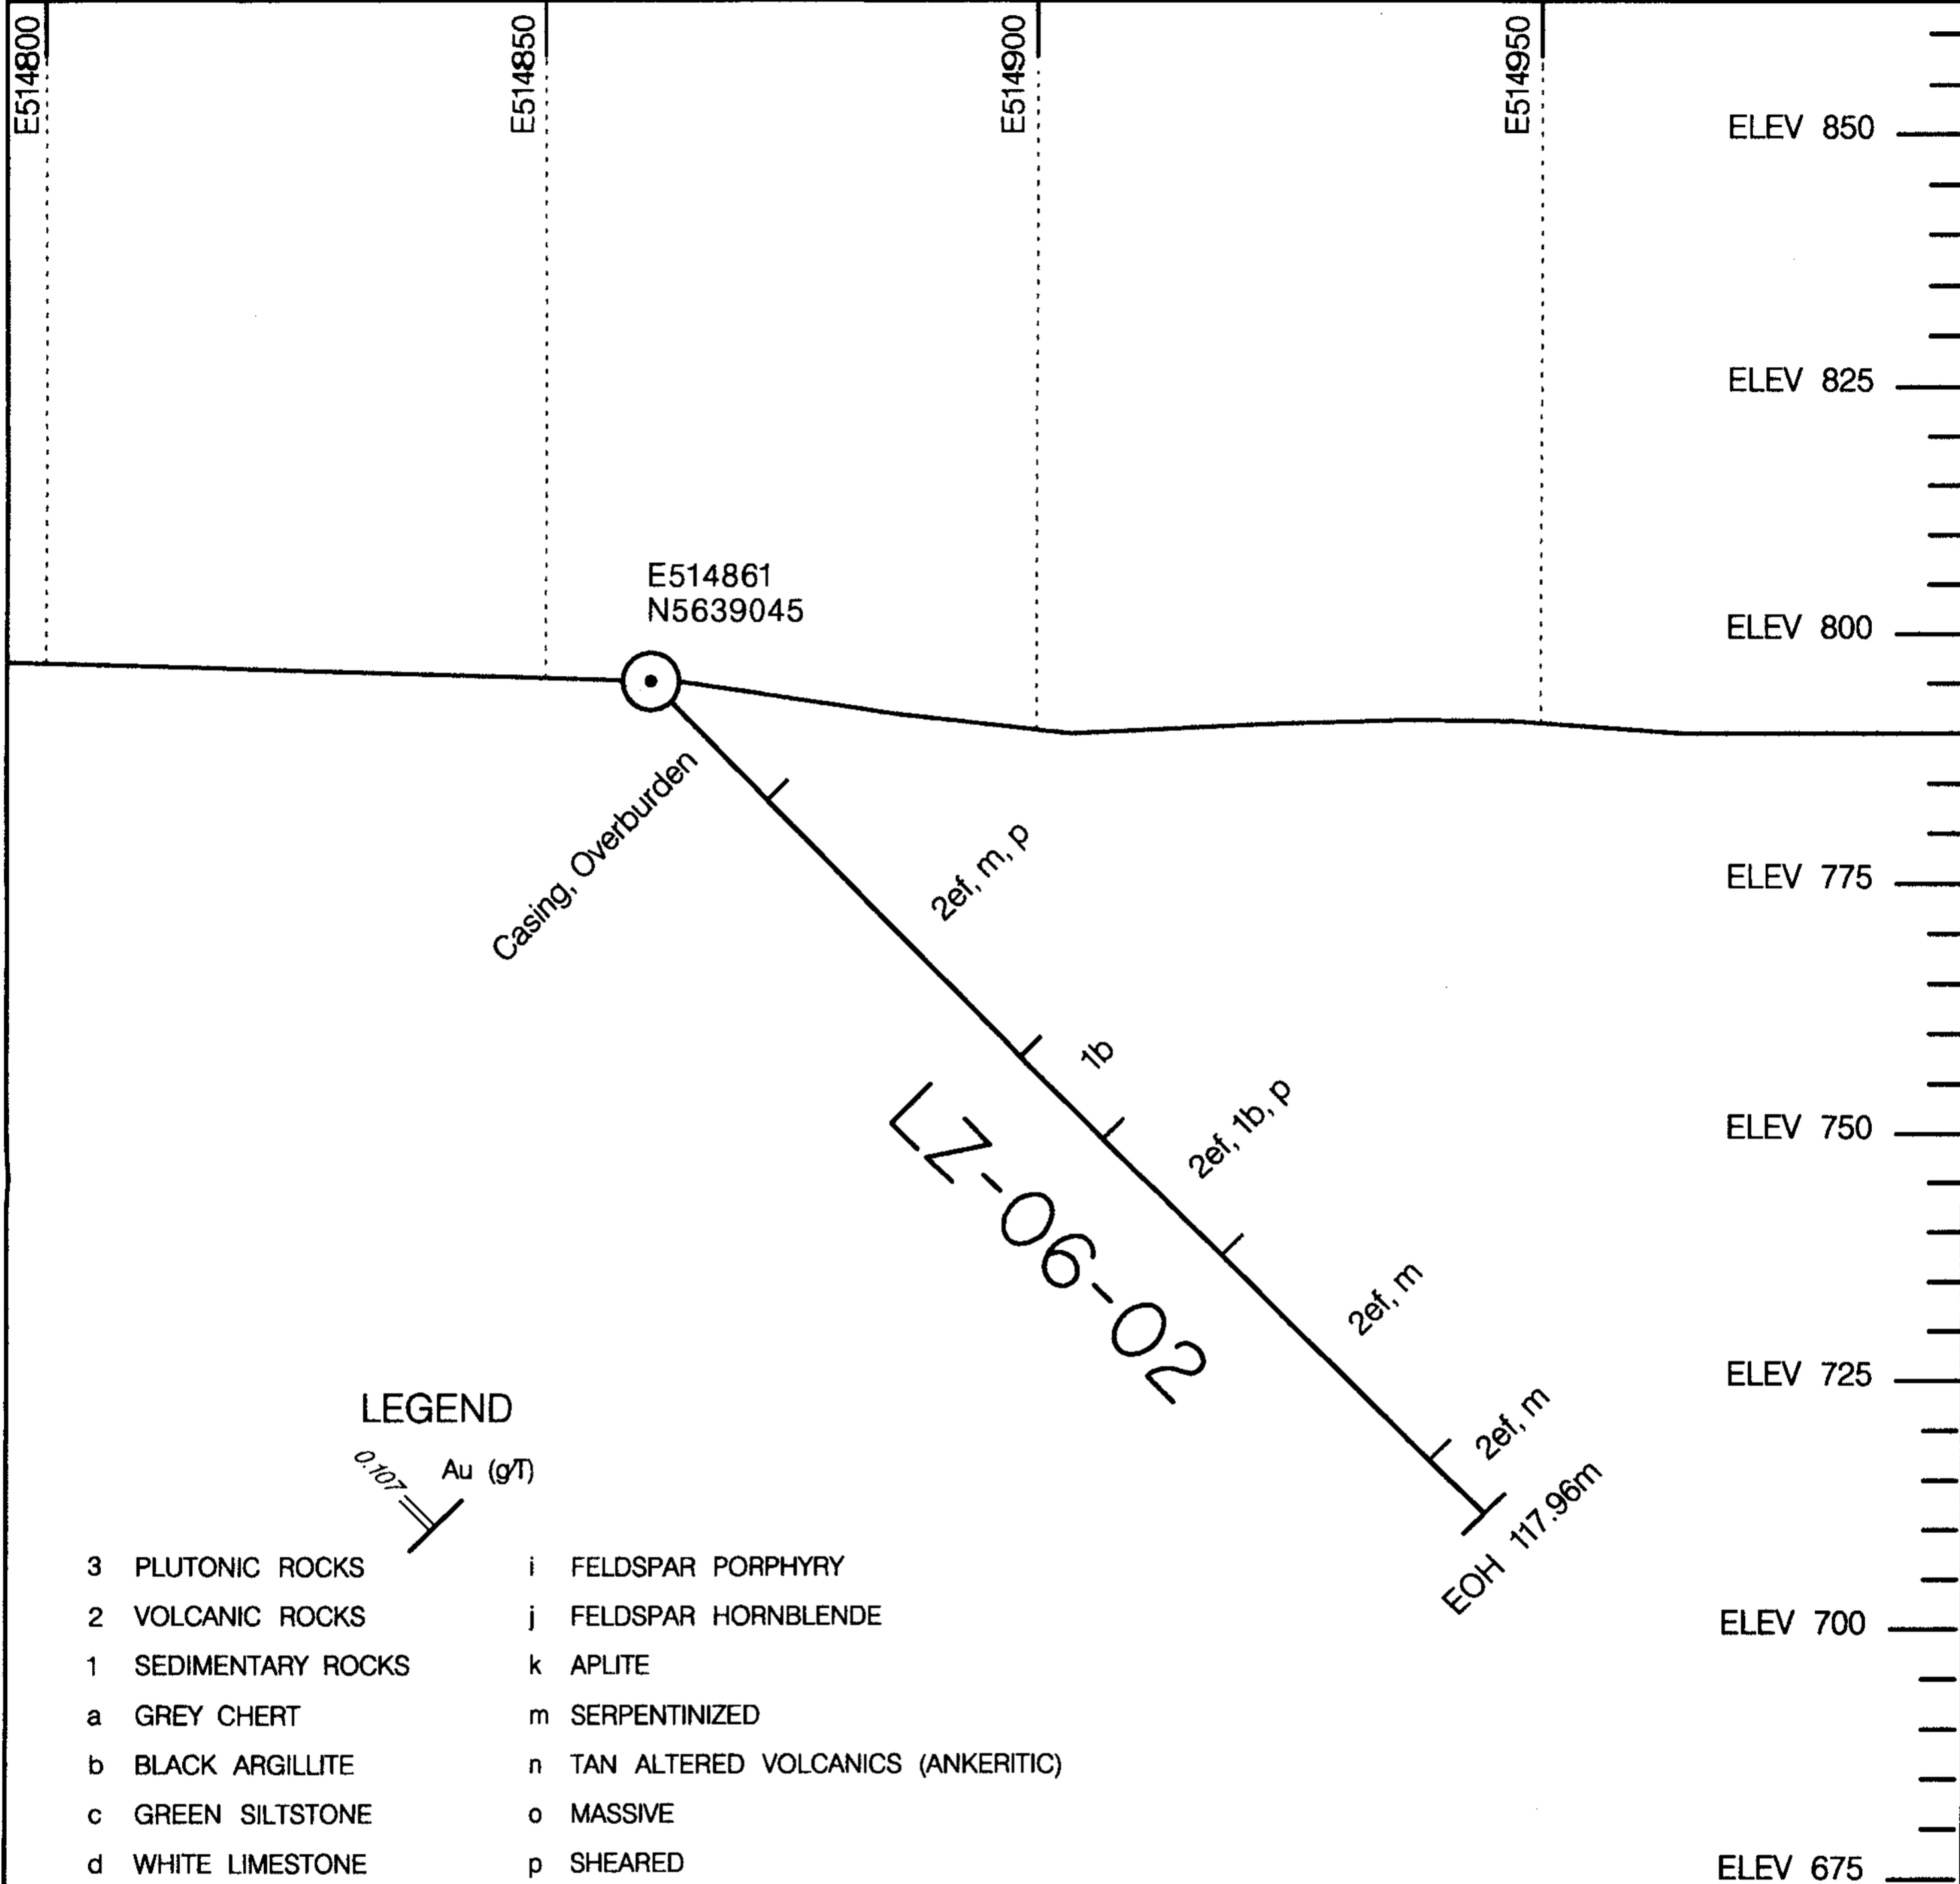

**LEGEND**

0.107 Au (gT)

- |                     |                                     |
|---------------------|-------------------------------------|
| 3 PLUTONIC ROCKS    | i FELDSPAR PORPHYRY                 |
| 2 VOLCANIC ROCKS    | j FELDSPAR HORNBLLENDE              |
| 1 SEDIMENTARY ROCKS | k APLITE                            |
| a GREY CHERT        | m SERPENTINIZED                     |
| b BLACK ARGILLITE   | n TAN ALTERED VOLCANICS (ANKERITIC) |
| c GREEN SILTSTONE   | o MASSIVE                           |
| d WHITE LIMESTONE   | p SHEARED                           |
| e GREEN BASALT      | q BEDDED                            |
| f PURPLE BASALT     | r JOINTED                           |
| g GREEN TUFF        | s PILLOWED                          |
| h GREEN GABBRO      | t AMYGDALOIDAL                      |

HOLE	AZIMUTH	DIP	EASTING	NORTHING	ELEVATION	LENGTH
LZ-06-02	90	-45	E514861	N5639045	795	117.96

Scale: 1:1000


Date: May 18, 2007



BCGS Mapsheet: 92J.097, NTS Mapsheet: 92J/15

File: CONGRESS\_LZ-06-02\_DDH-Section\_8x11\_1k\_2007-05-18

**CONGRESS PROPERTY - LOU ZONE**  
**DDH SECTION LZ-06-03**  
**LOOKING NORTH**

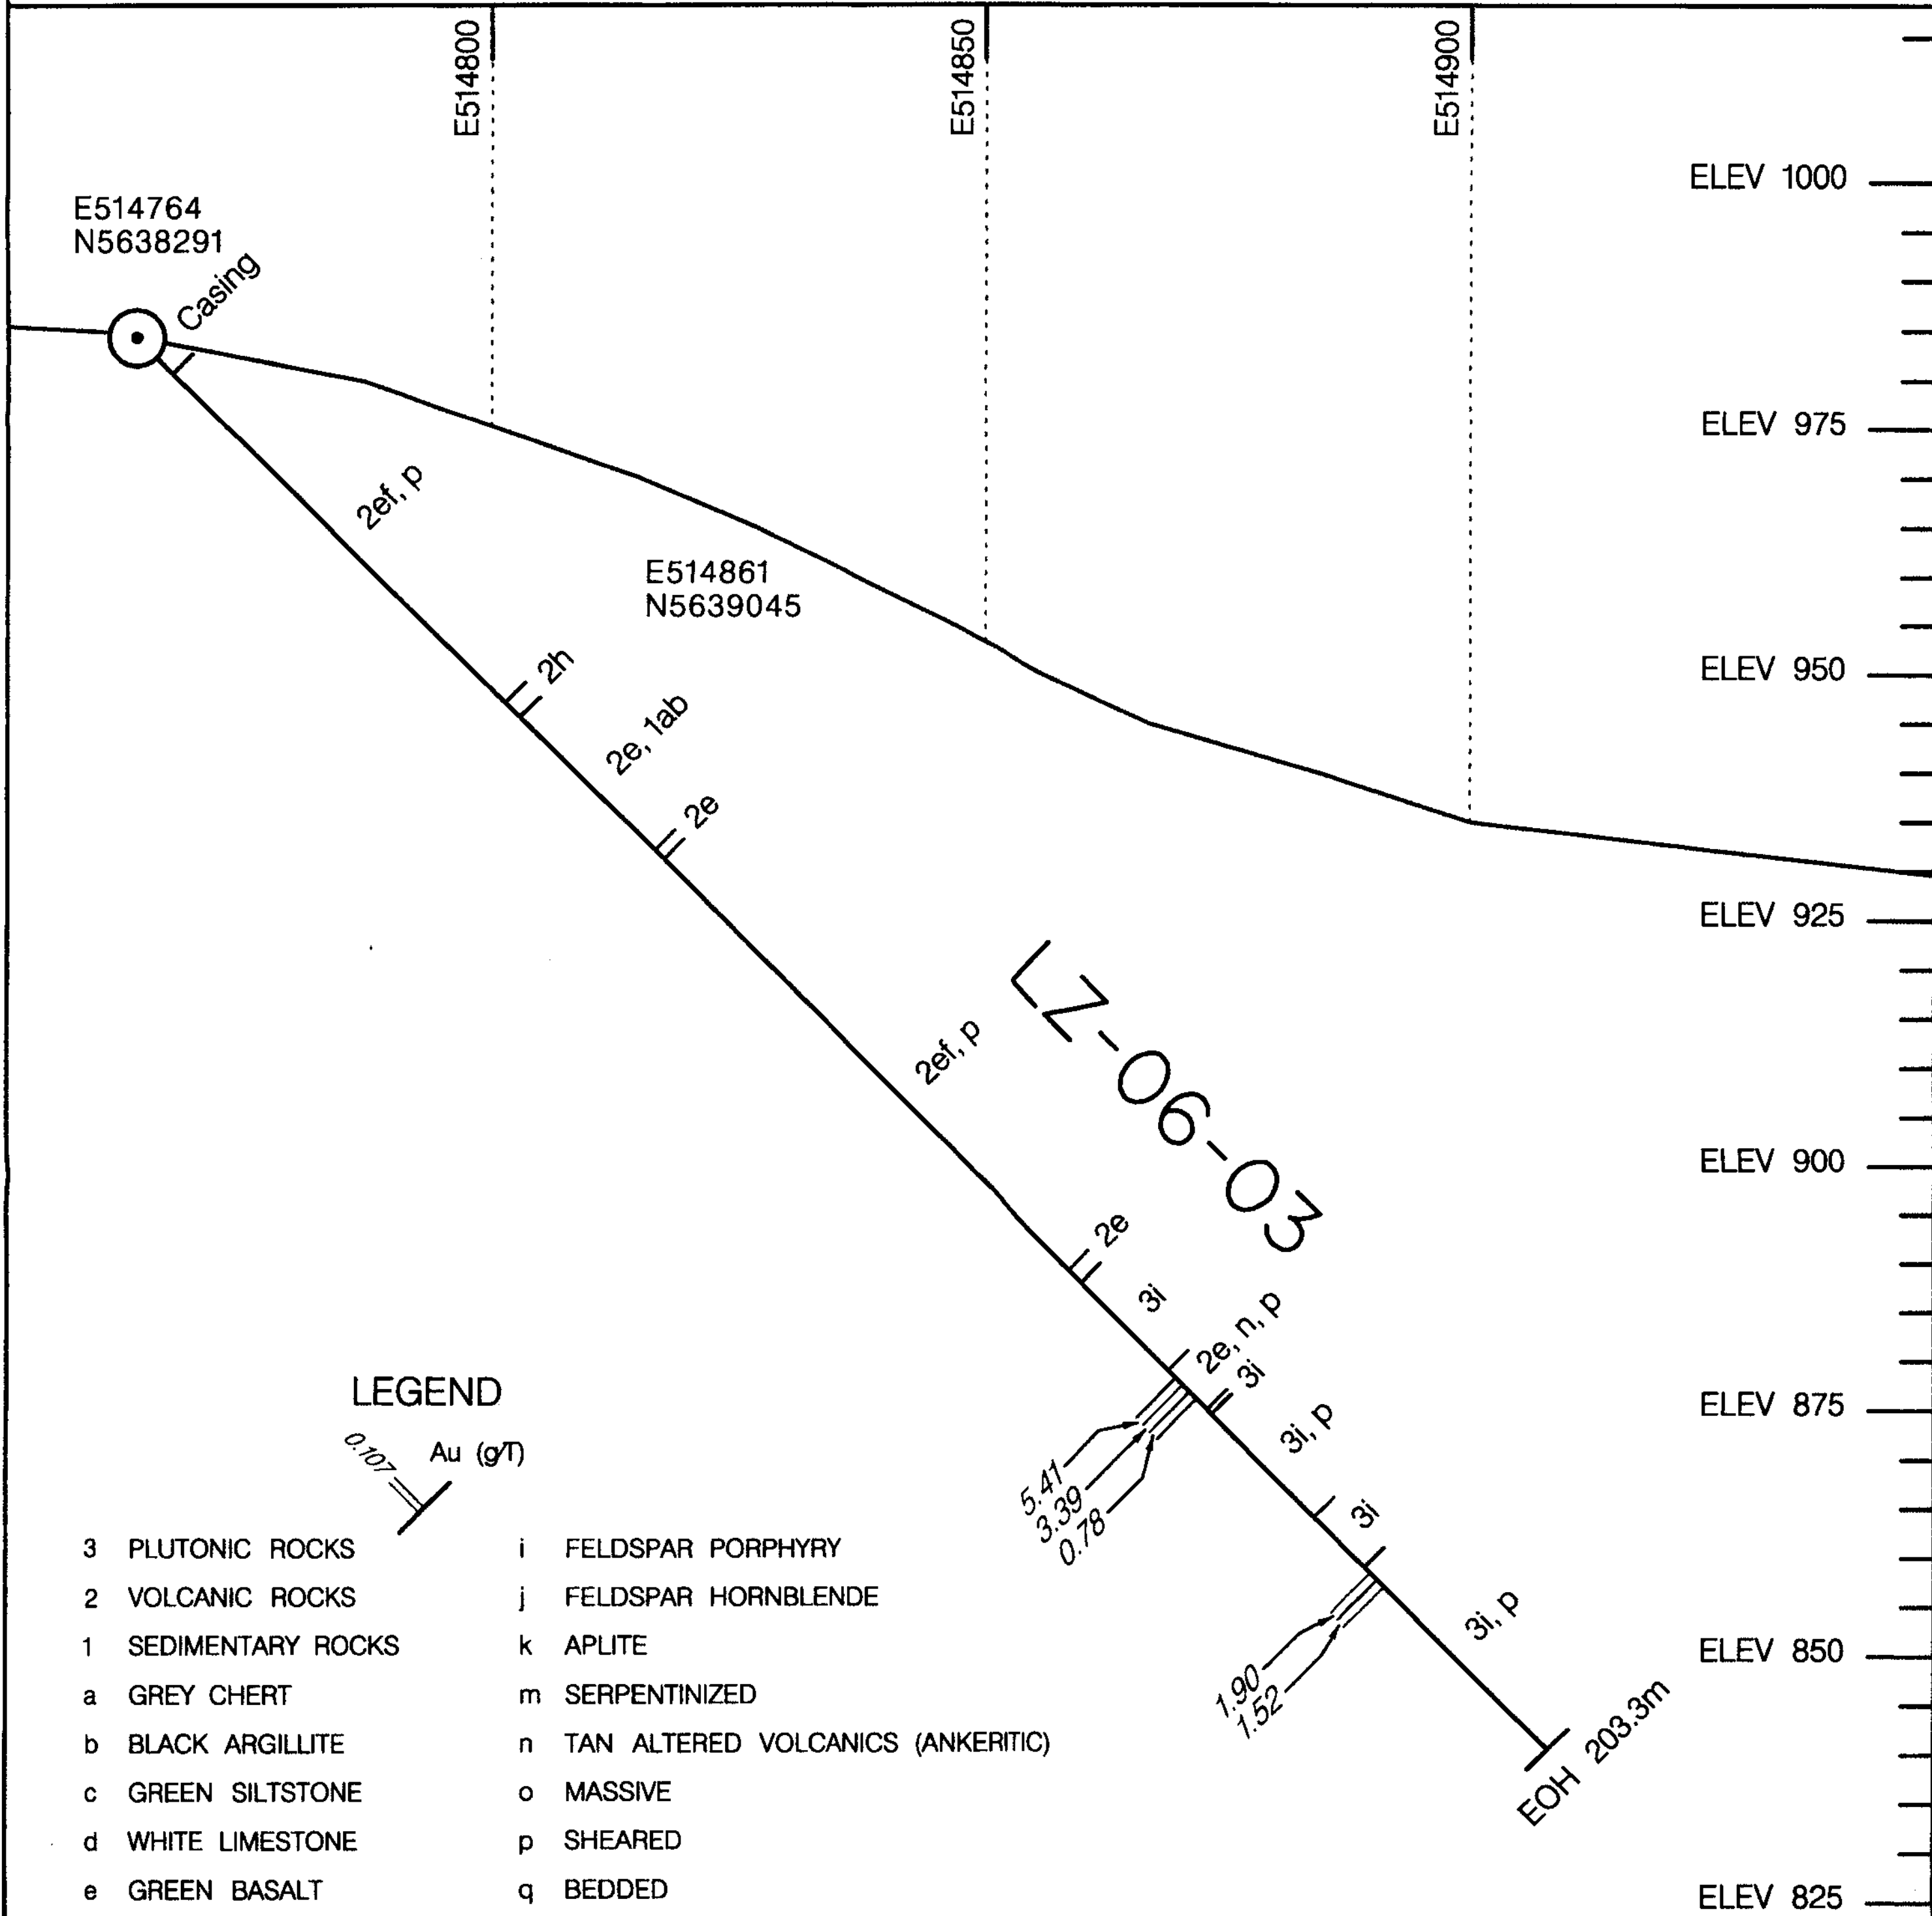

**LEGEND**


0.107 Au (g/T)


- |                     |                                     |
|---------------------|-------------------------------------|
| 3 PLUTONIC ROCKS    | i FELDSPAR PORPHYRY                 |
| 2 VOLCANIC ROCKS    | j FELDSPAR HORNBLLENDE              |
| 1 SEDIMENTARY ROCKS | k APLITE                            |
| a GREY CHERT        | m SERPENTINIZED                     |
| b BLACK ARGILLITE   | n TAN ALTERED VOLCANICS (ANKERITIC) |
| c GREEN SILTSTONE   | o MASSIVE                           |
| d WHITE LIMESTONE   | p SHEARED                           |
| e GREEN BASALT      | q BEDDED                            |
| f PURPLE BASALT     | r JOINTED                           |
| g GREEN TUFF        | s PILLOWED                          |
| h GREEN GABBRO      | t AMYGDALOIDAL                      |

HOLE	AZIMUTH	DIP	EASTING	NORTHING	ELEVATION	LENGTH
LZ-06-03	90	-45	E514764	N5638291	985	203.3

Scale: 1:1000 Date: May 18, 2007  
0 10 20 30 40 50 Metres

**CONGRESS PROPERTY - LOU ZONE**  
**DDH SECTION LZ-06-04**  
**LOOKING NORTH**

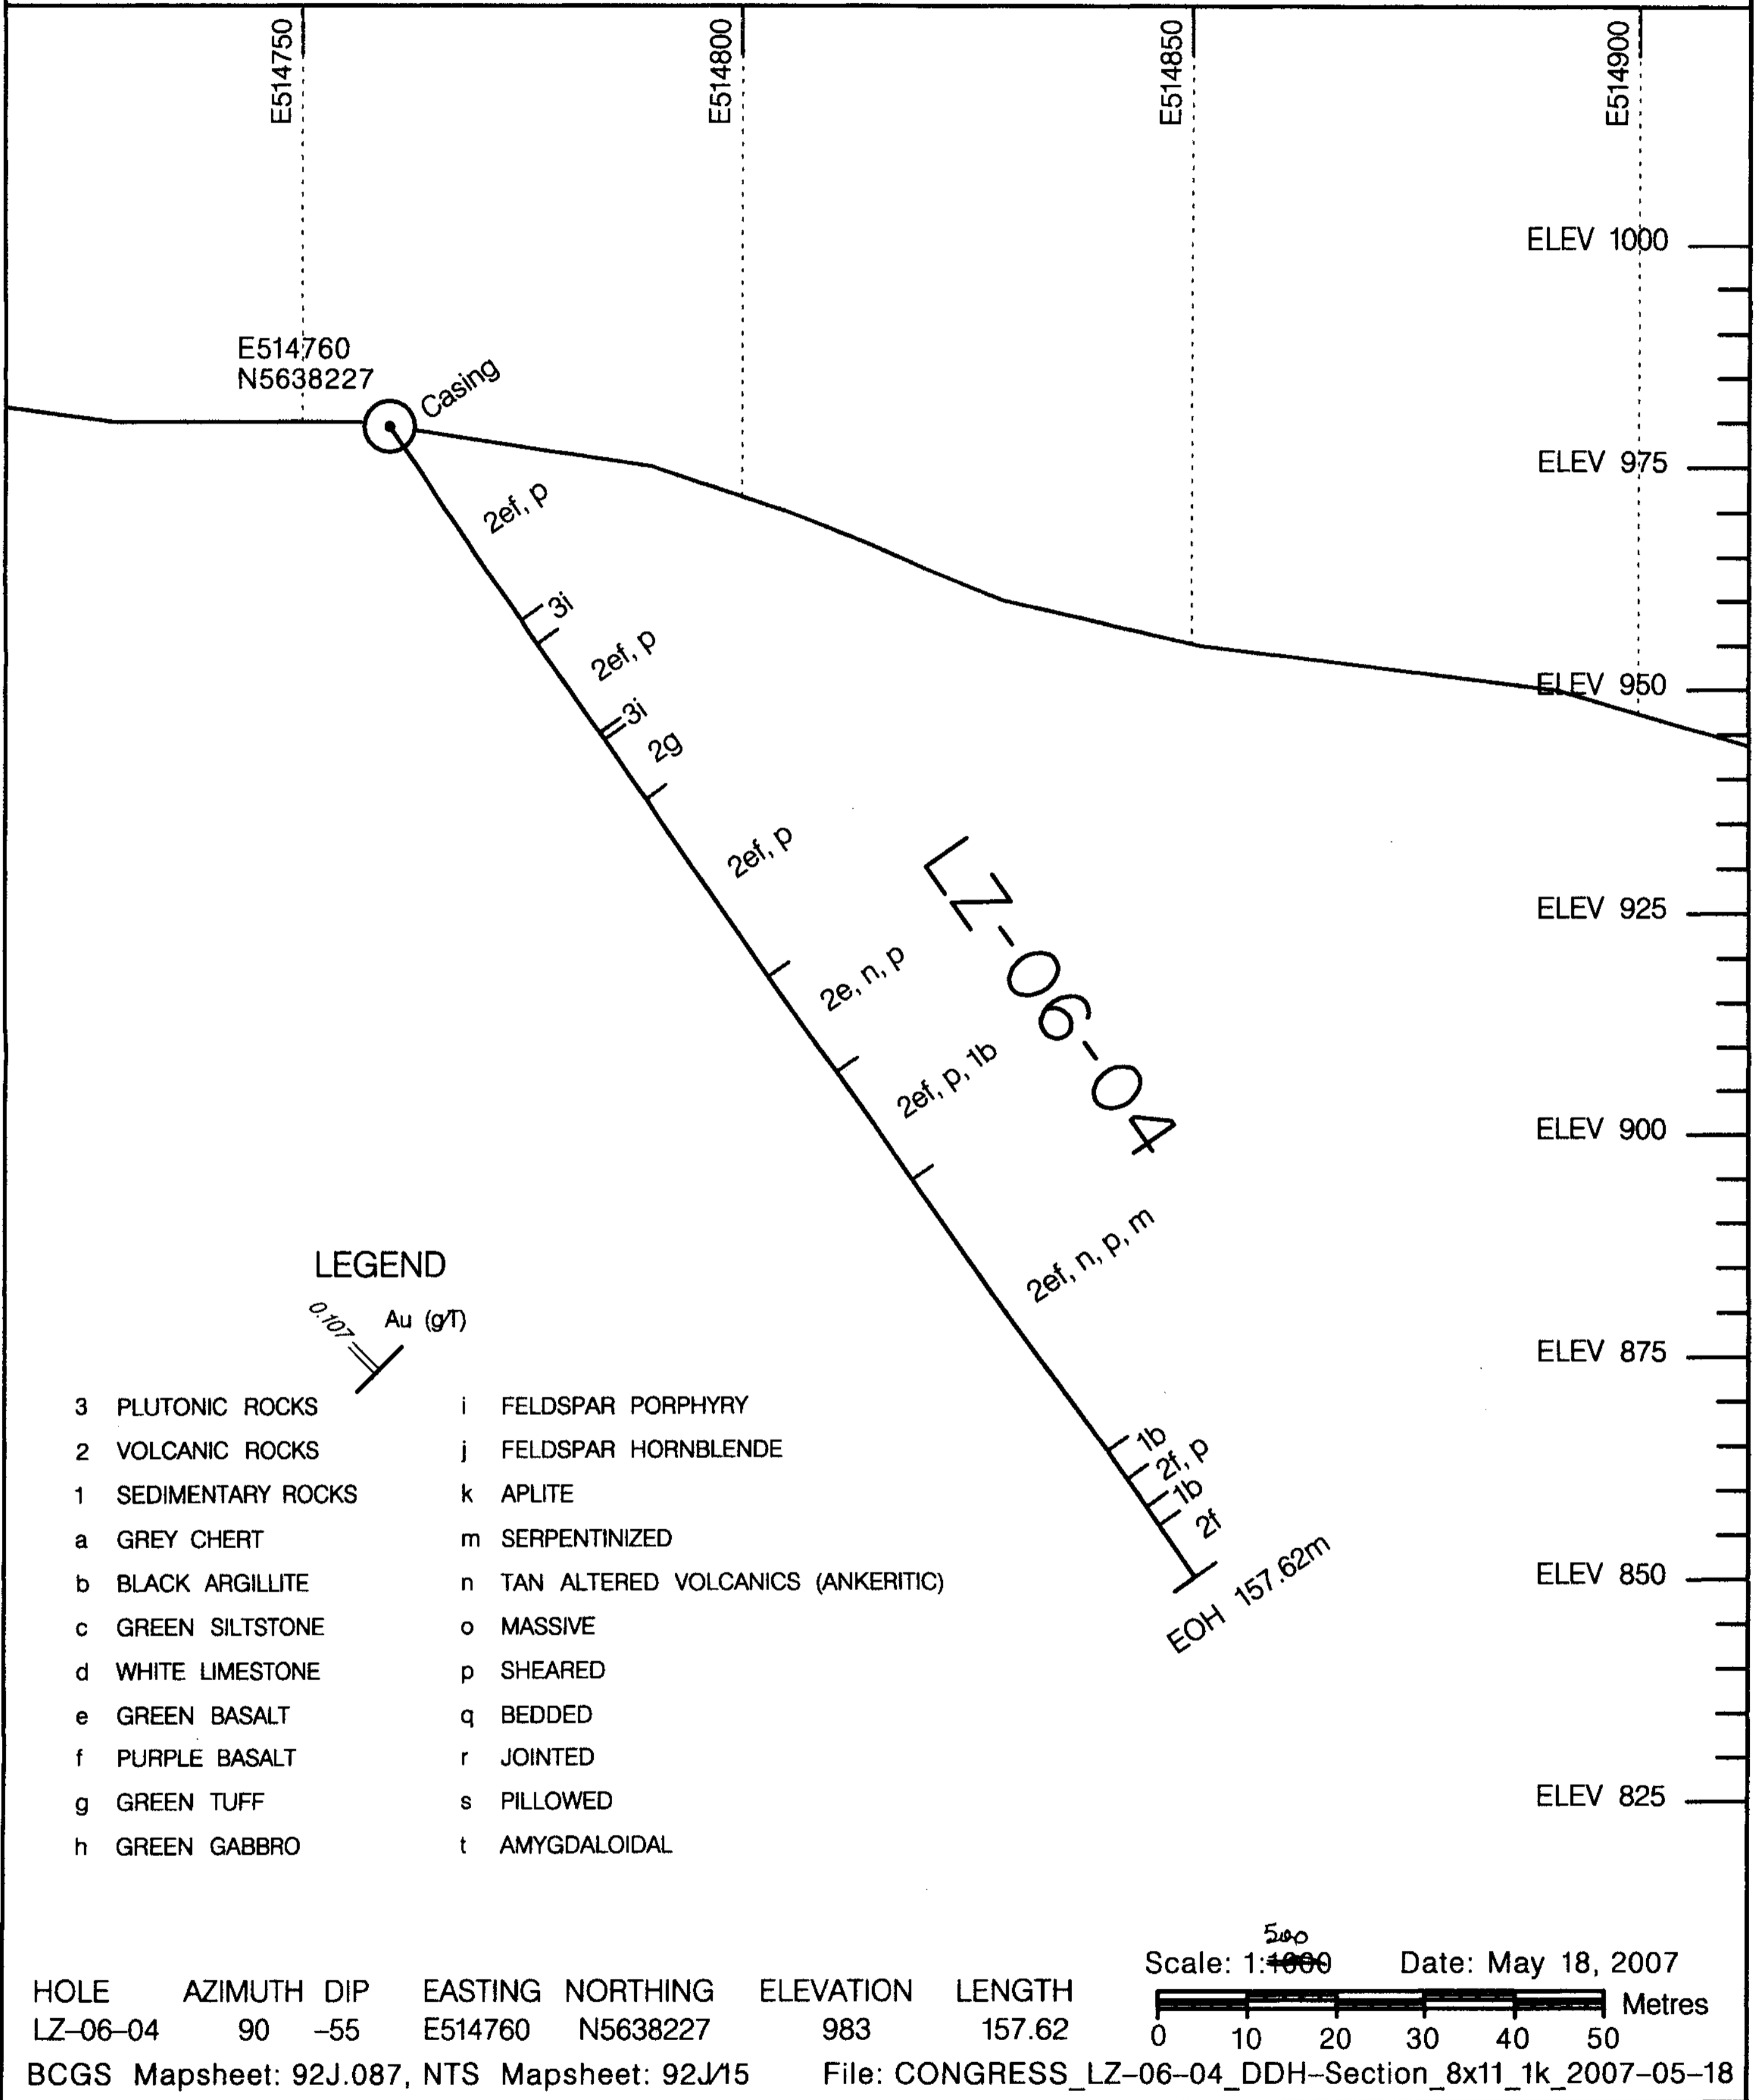

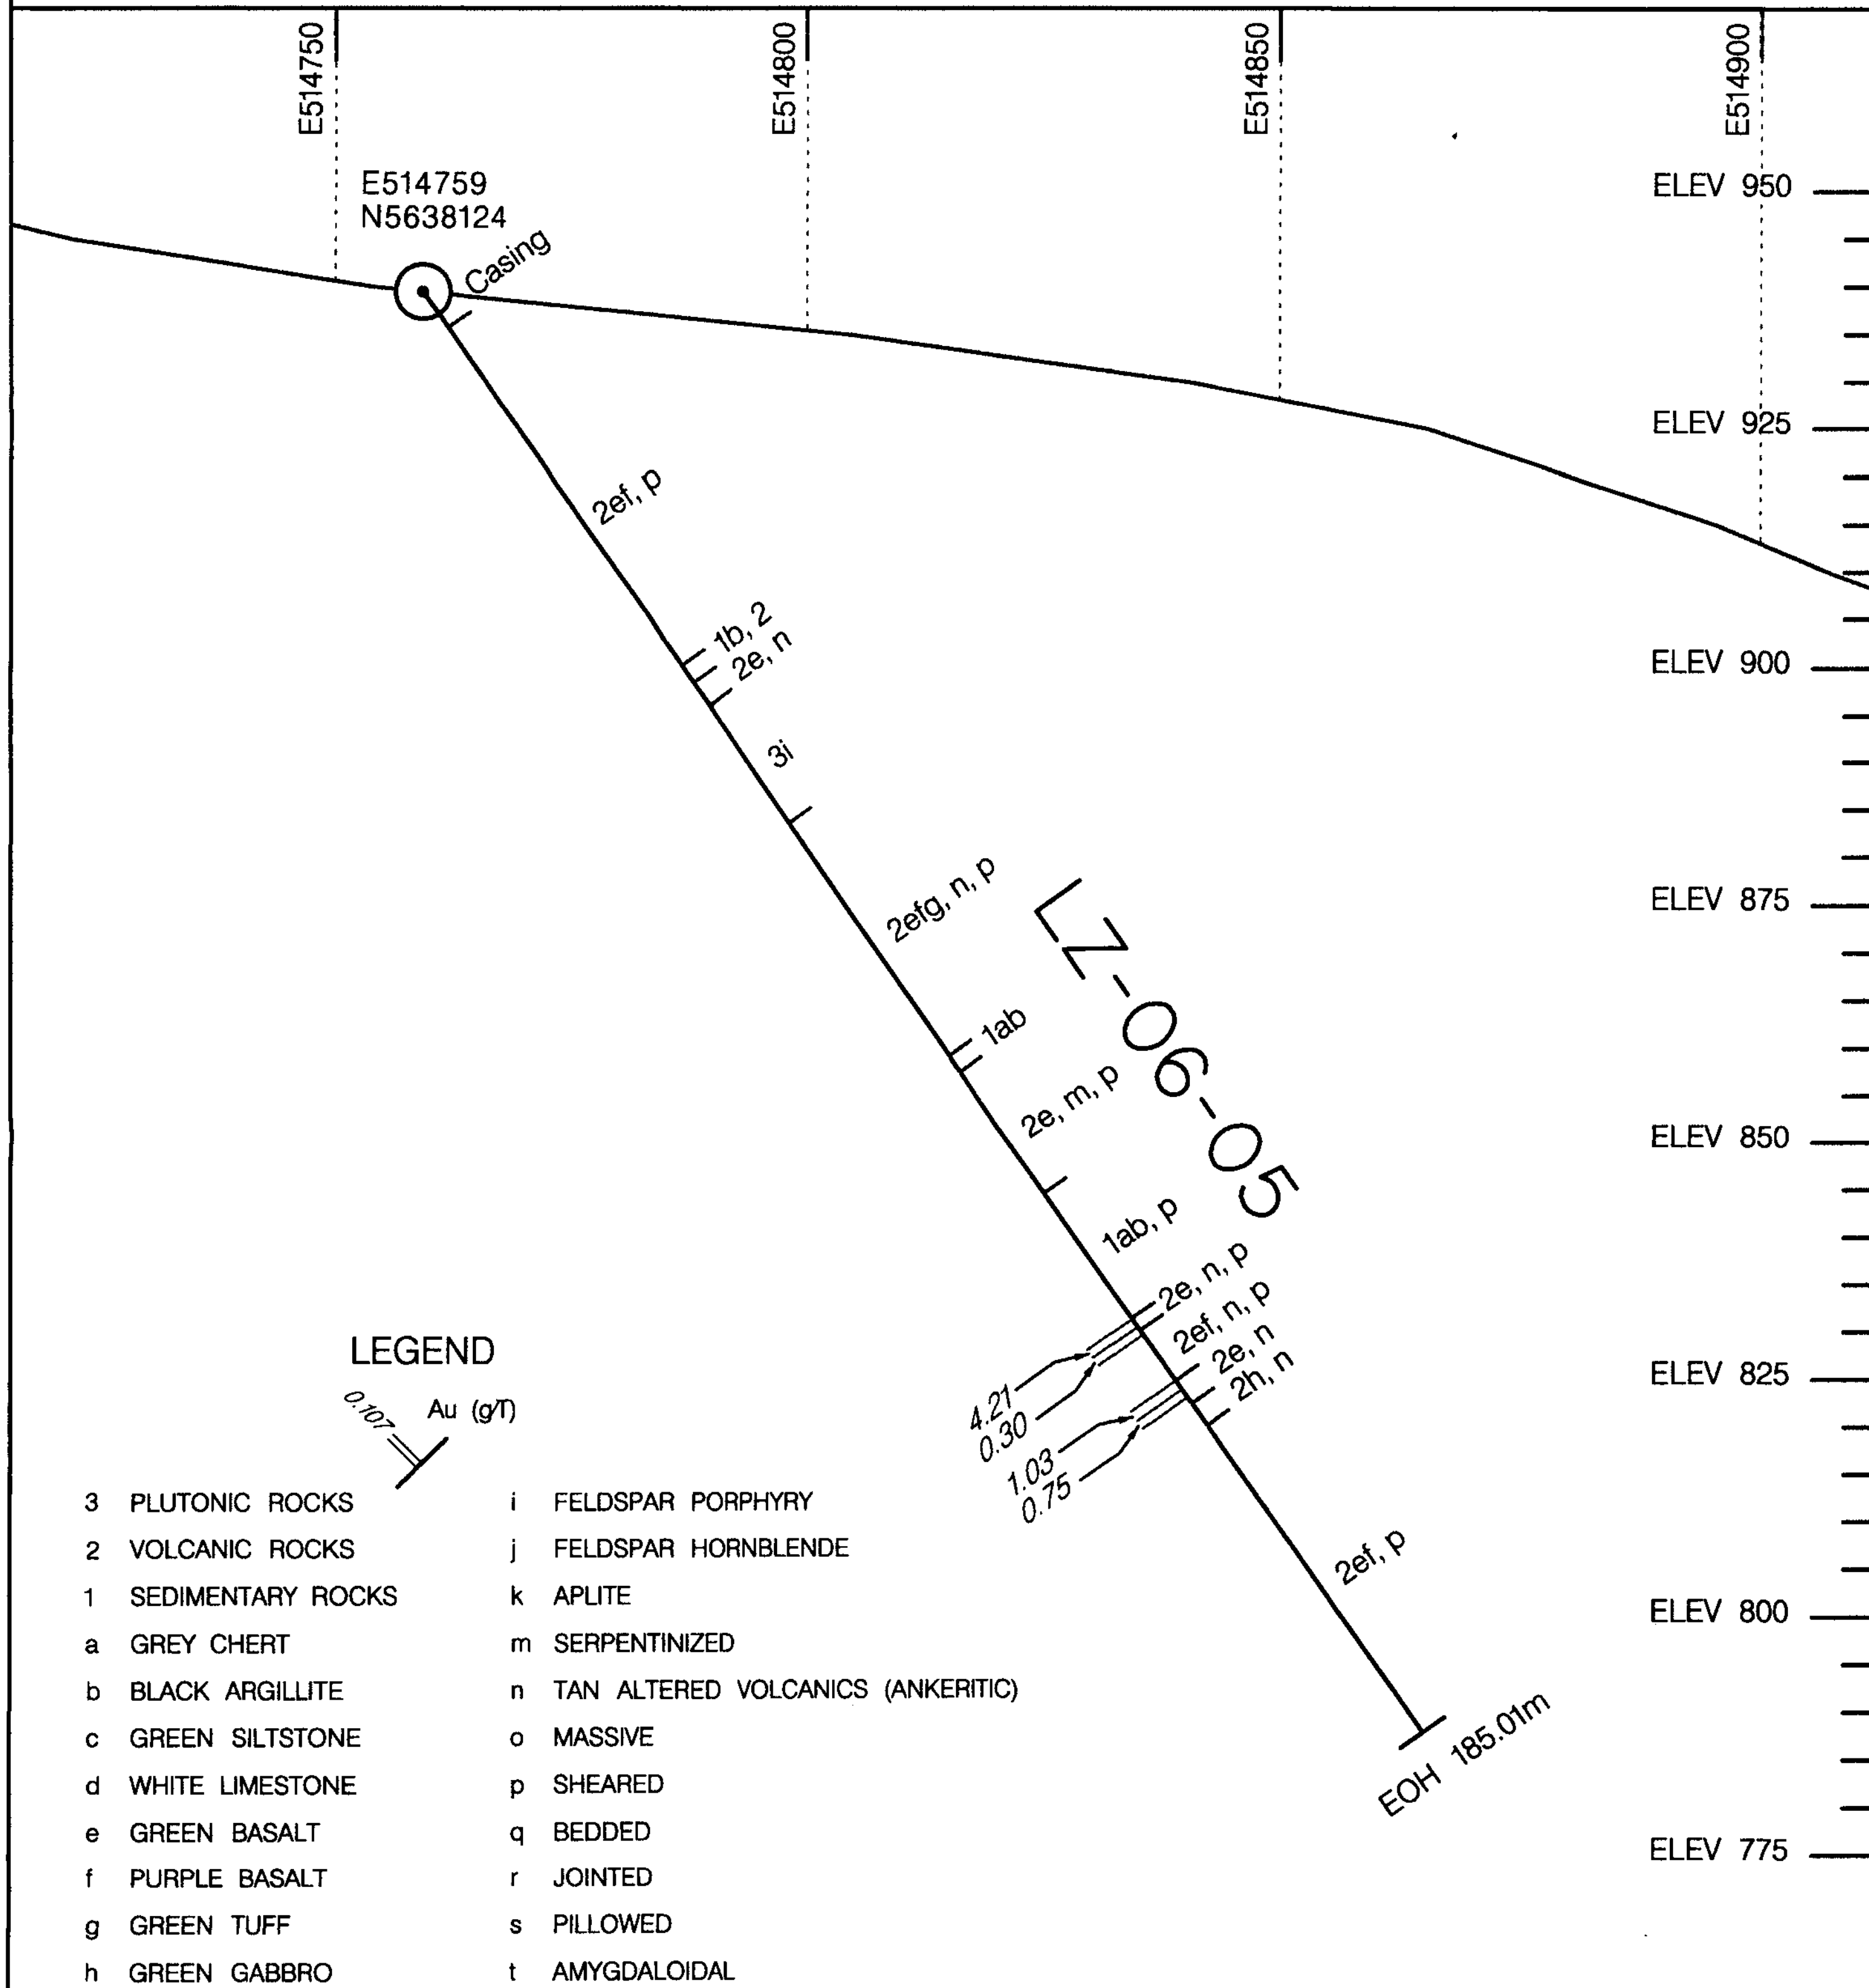


**LEGEND**

0.107 Au (g/T)

- |                     |                                     |
|---------------------|-------------------------------------|
| 3 PLUTONIC ROCKS    | i FELDSPAR PORPHYRY                 |
| 2 VOLCANIC ROCKS    | j FELDSPAR HORNBLENDE               |
| 1 SEDIMENTARY ROCKS | k APLITE                            |
| a GREY CHERT        | m SERPENTINIZED                     |
| b BLACK ARGILLITE   | n TAN ALTERED VOLCANICS (ANKERITIC) |
| c GREEN SILTSTONE   | o MASSIVE                           |
| d WHITE LIMESTONE   | p SHEARED                           |
| e GREEN BASALT      | q BEDDED                            |
| f PURPLE BASALT     | r JOINTED                           |
| g GREEN TUFF        | s PILLOWED                          |
| h GREEN GABBRO      | t AMYGDALOIDAL                      |

HOLE	AZIMUTH	DIP	EASTING	NORTHING	ELEVATION	LENGTH	Scale: 1: <del>1000</del> <sup>500</sup>	Date: May 18, 2007
LZ-06-05	90	-55	E514759	N5638124	942	185.01		
BCGS Mapsheet: 92J.087, NTS Mapsheet: 92J/15							File: CONGRESS_LZ-06-05_DDH-Section_8x11_1k_2007-05-18	

**CONGRESS PROPERTY - LOU ZONE**  
**DDH SECTION LZ-06-06**  
**LOOKING NORTH (6 Degrees)**

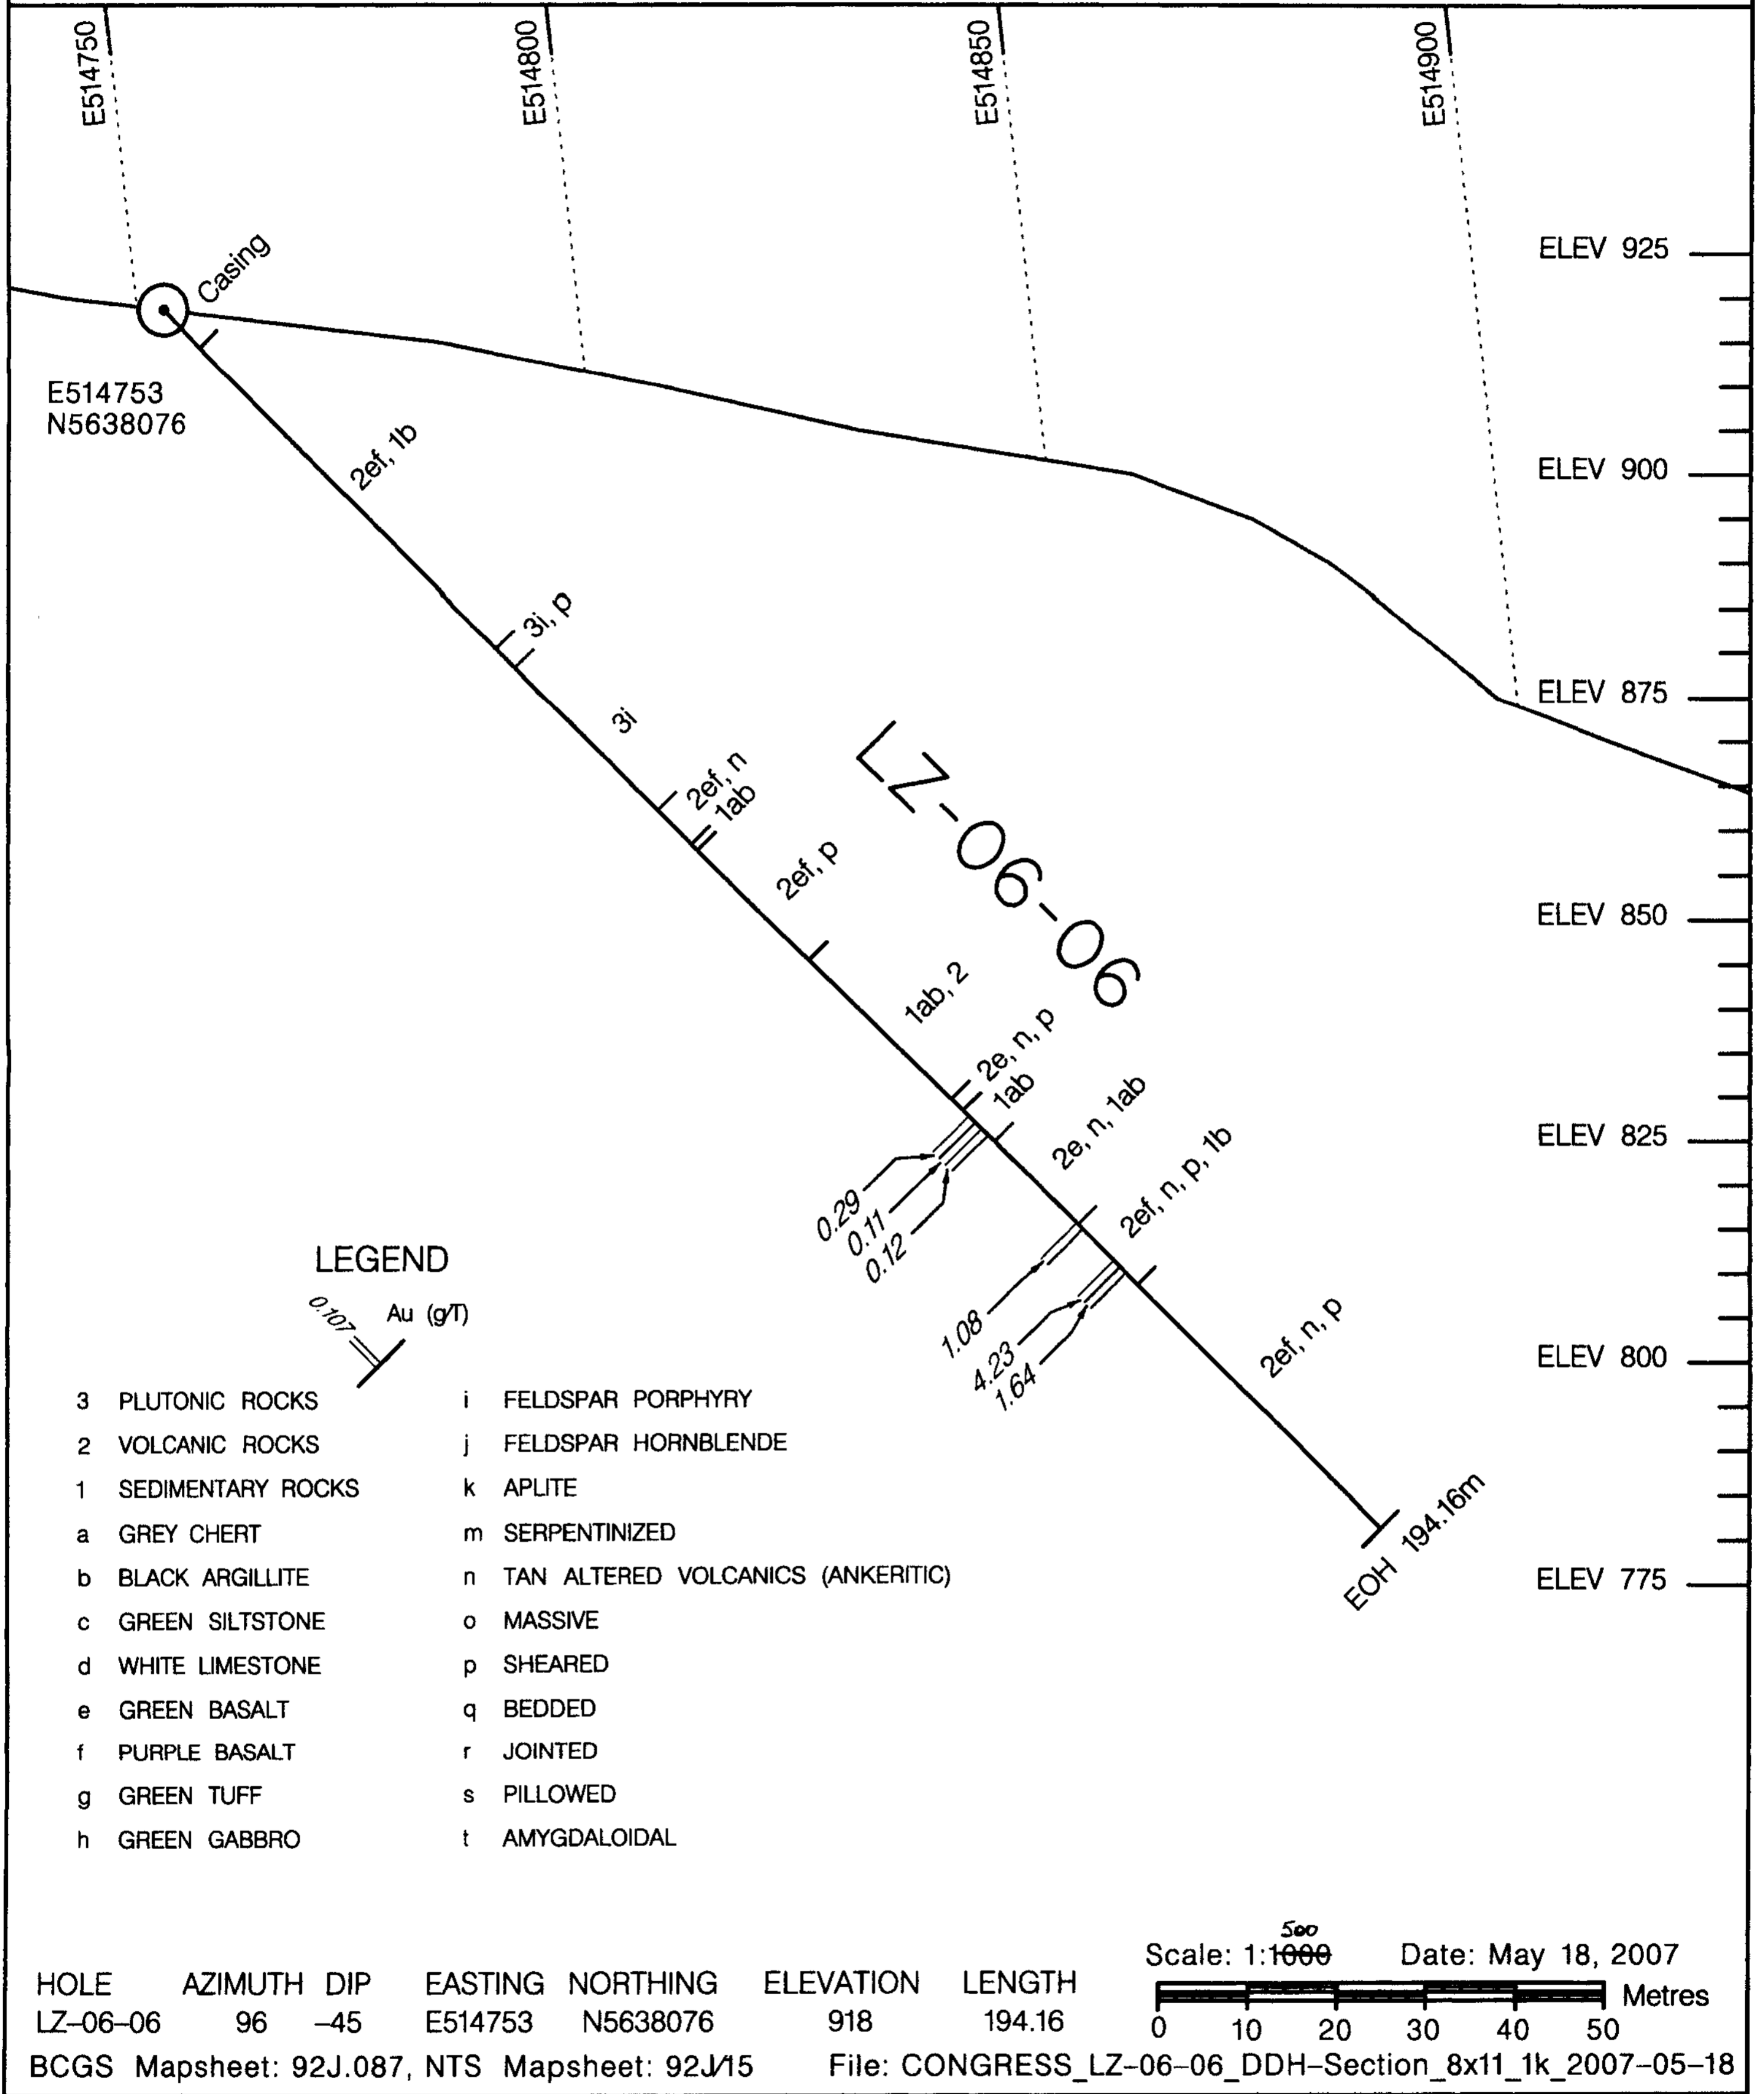

**LEGEND**


0.107 Au (g/T)

- |                     |                                     |
|---------------------|-------------------------------------|
| 3 PLUTONIC ROCKS    | i FELDSPAR PORPHYRY                 |
| 2 VOLCANIC ROCKS    | j FELDSPAR HORNBLLENDE              |
| 1 SEDIMENTARY ROCKS | k APLITE                            |
| a GREY CHERT        | m SERPENTINIZED                     |
| b BLACK ARGILLITE   | n TAN ALTERED VOLCANICS (ANKERITIC) |
| c GREEN SILTSTONE   | o MASSIVE                           |
| d WHITE LIMESTONE   | p SHEARED                           |
| e GREEN BASALT      | q BEDDED                            |
| f PURPLE BASALT     | r JOINTED                           |
| g GREEN TUFF        | s PILLOWED                          |
| h GREEN GABBRO      | t AMYGDALOIDAL                      |

HOLE	AZIMUTH	DIP	EASTING	NORTHING	ELEVATION	LENGTH
LZ-06-06	96	-45	E514753	N5638076	918	194.16

Scale: 1:1000 Date: May 18, 2007  
0 10 20 30 40 50 Metres

**CONGRESS PROPERTY - LOU ZONE**  
**DDH SECTION LZ-06-07**  
**LOOKING NORTH (16 Degrees)**

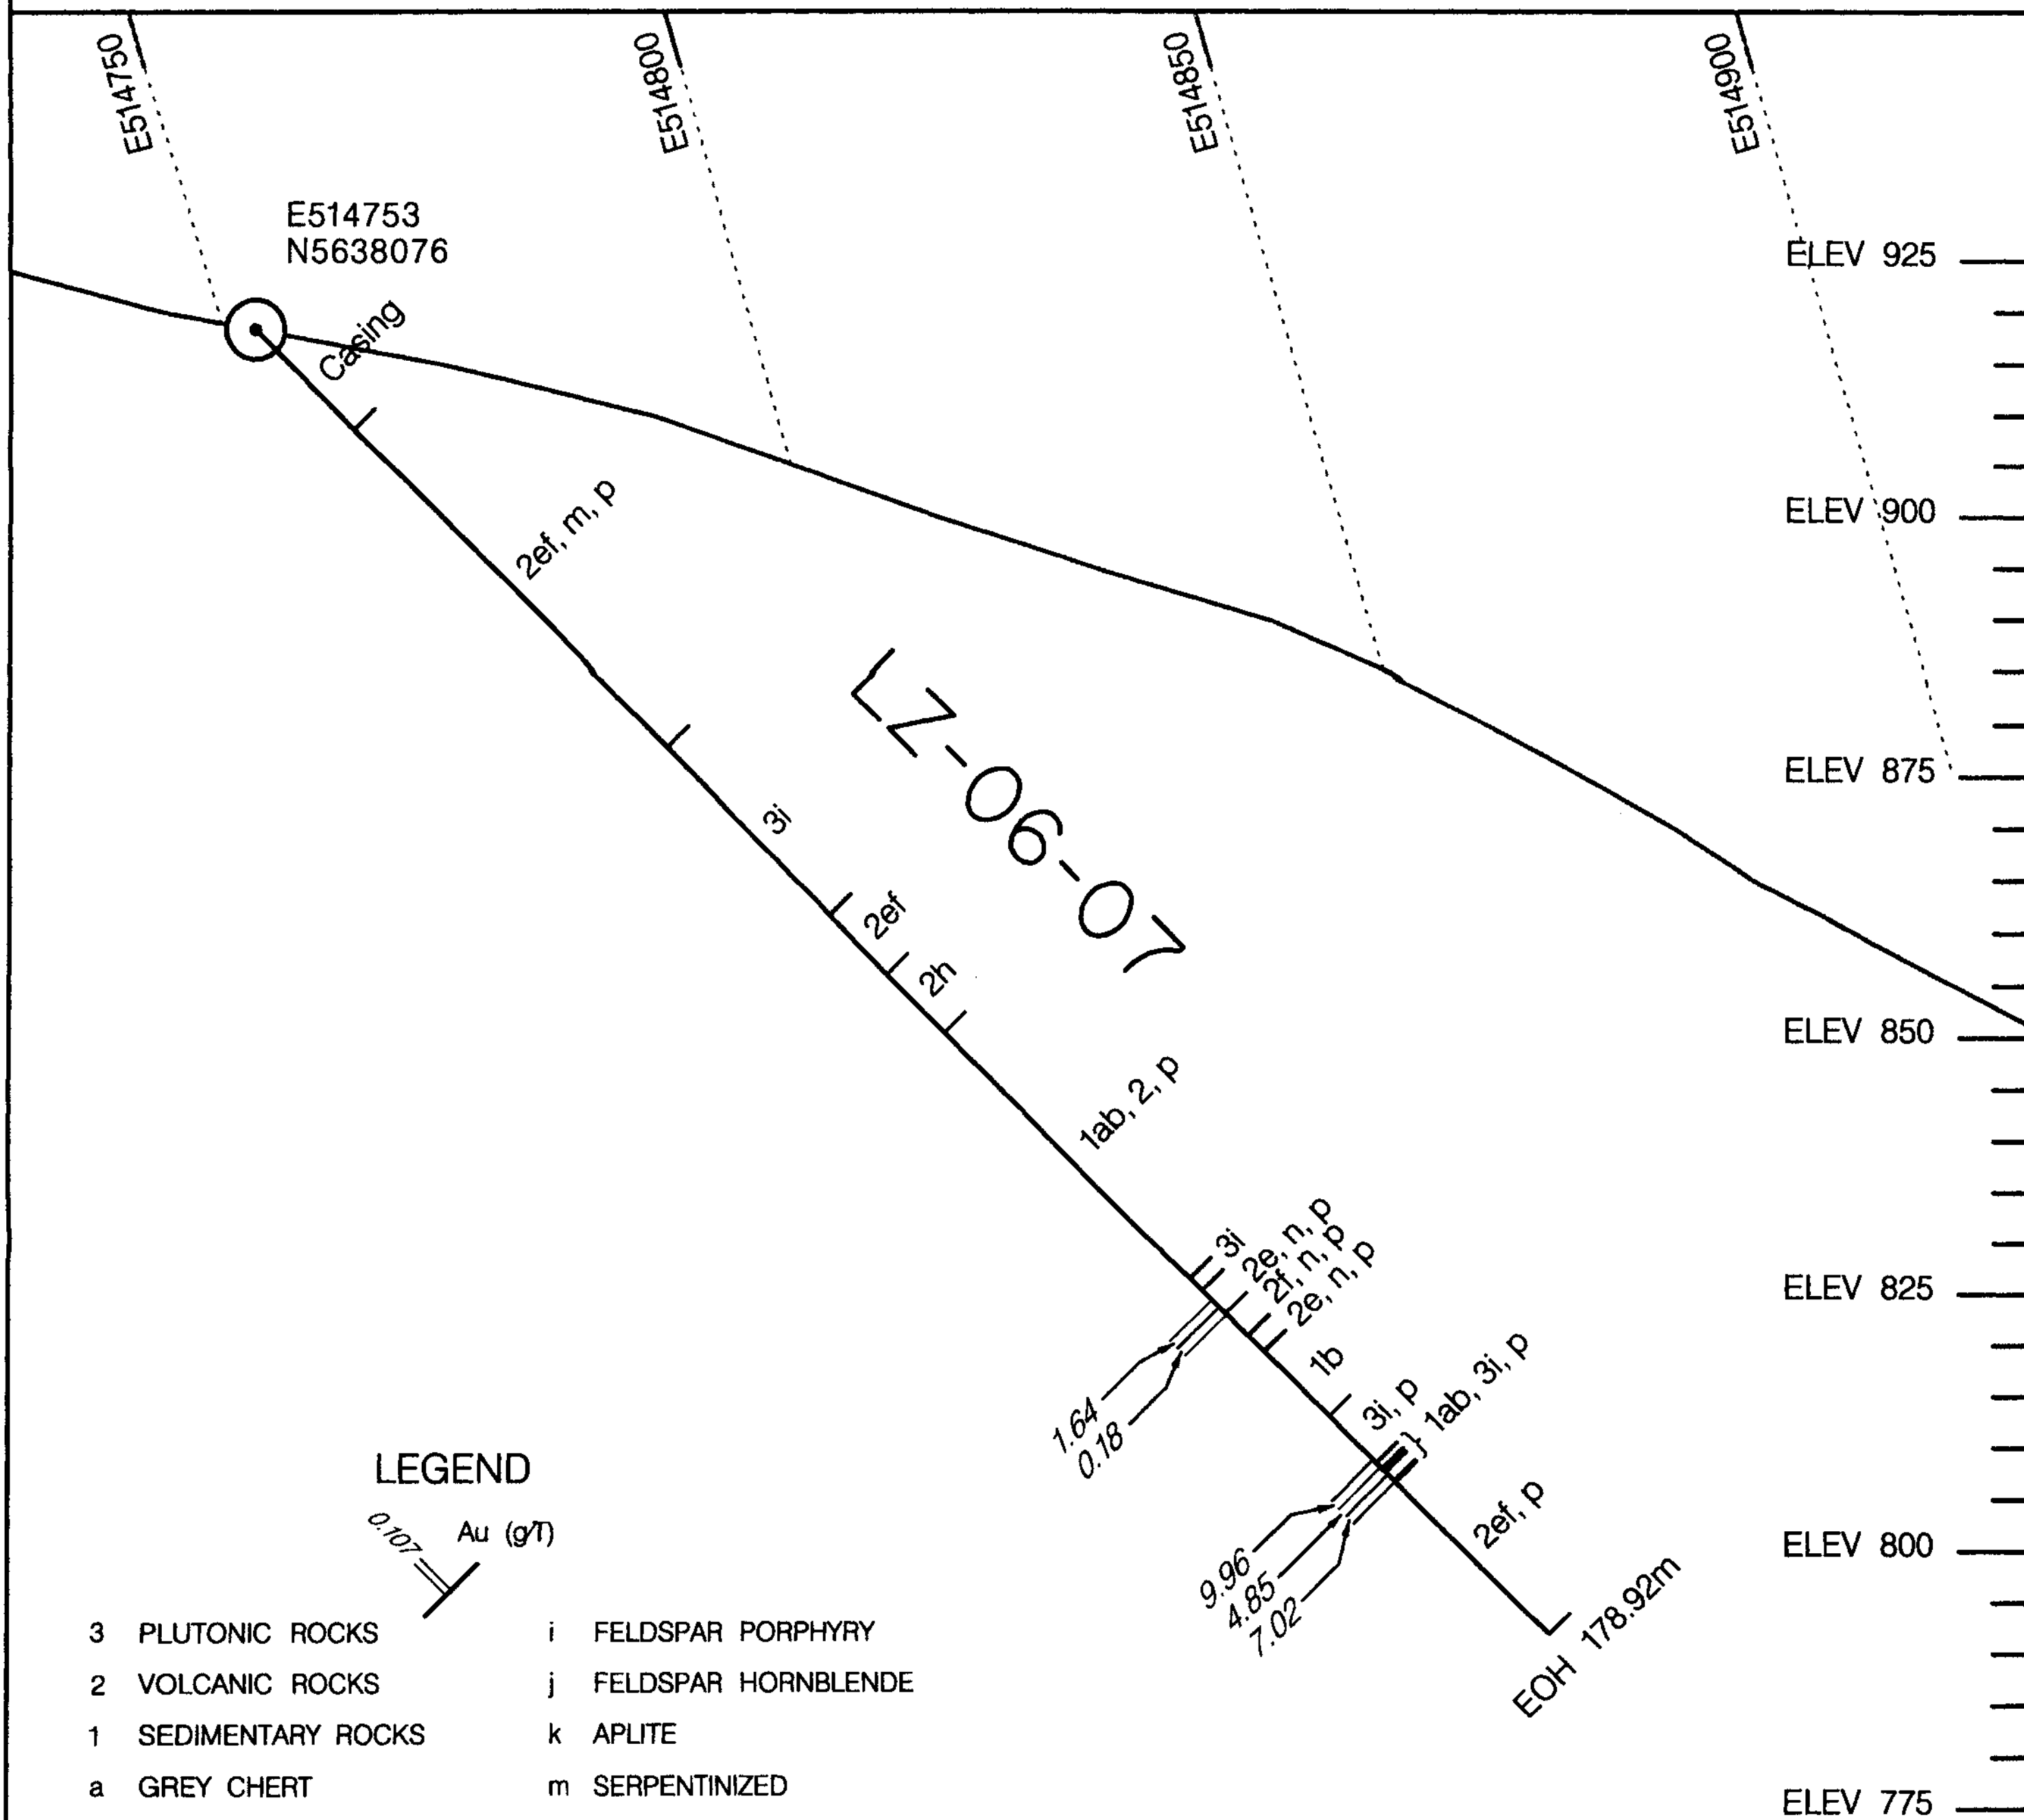

**LEGEND**

0.107 Au (gT)


- |                     |                                     |
|---------------------|-------------------------------------|
| 3 PLUTONIC ROCKS    | i FELDSPAR PORPHYRY                 |
| 2 VOLCANIC ROCKS    | j FELDSPAR HORNBLLENDE              |
| 1 SEDIMENTARY ROCKS | k APLITE                            |
| a GREY CHERT        | m SERPENTINIZED                     |
| b BLACK ARGILLITE   | n TAN ALTERED VOLCANICS (ANKERITIC) |
| c GREEN SILTSTONE   | o MASSIVE                           |
| d WHITE LIMESTONE   | p SHEARED                           |
| e GREEN BASALT      | q BEDDED                            |
| f PURPLE BASALT     | r JOINTED                           |
| g GREEN TUFF        | s PILLOWED                          |
| h GREEN GABBRO      | t AMYGDALOIDAL                      |

HOLE	AZIMUTH	DIP	EASTING	NORTHING	ELEVATION	LENGTH
LZ-06-07	106	-45	E514753	N5638076	918	178.92

Scale: 1:1000 Date: May 18, 2007

0 10 20 30 40 50 Metres

**CONGRESS PROPERTY - LOU ZONE**  
**DDH SECTION LZ-06-08**  
**LOOKING NORTH (16 Degrees)**

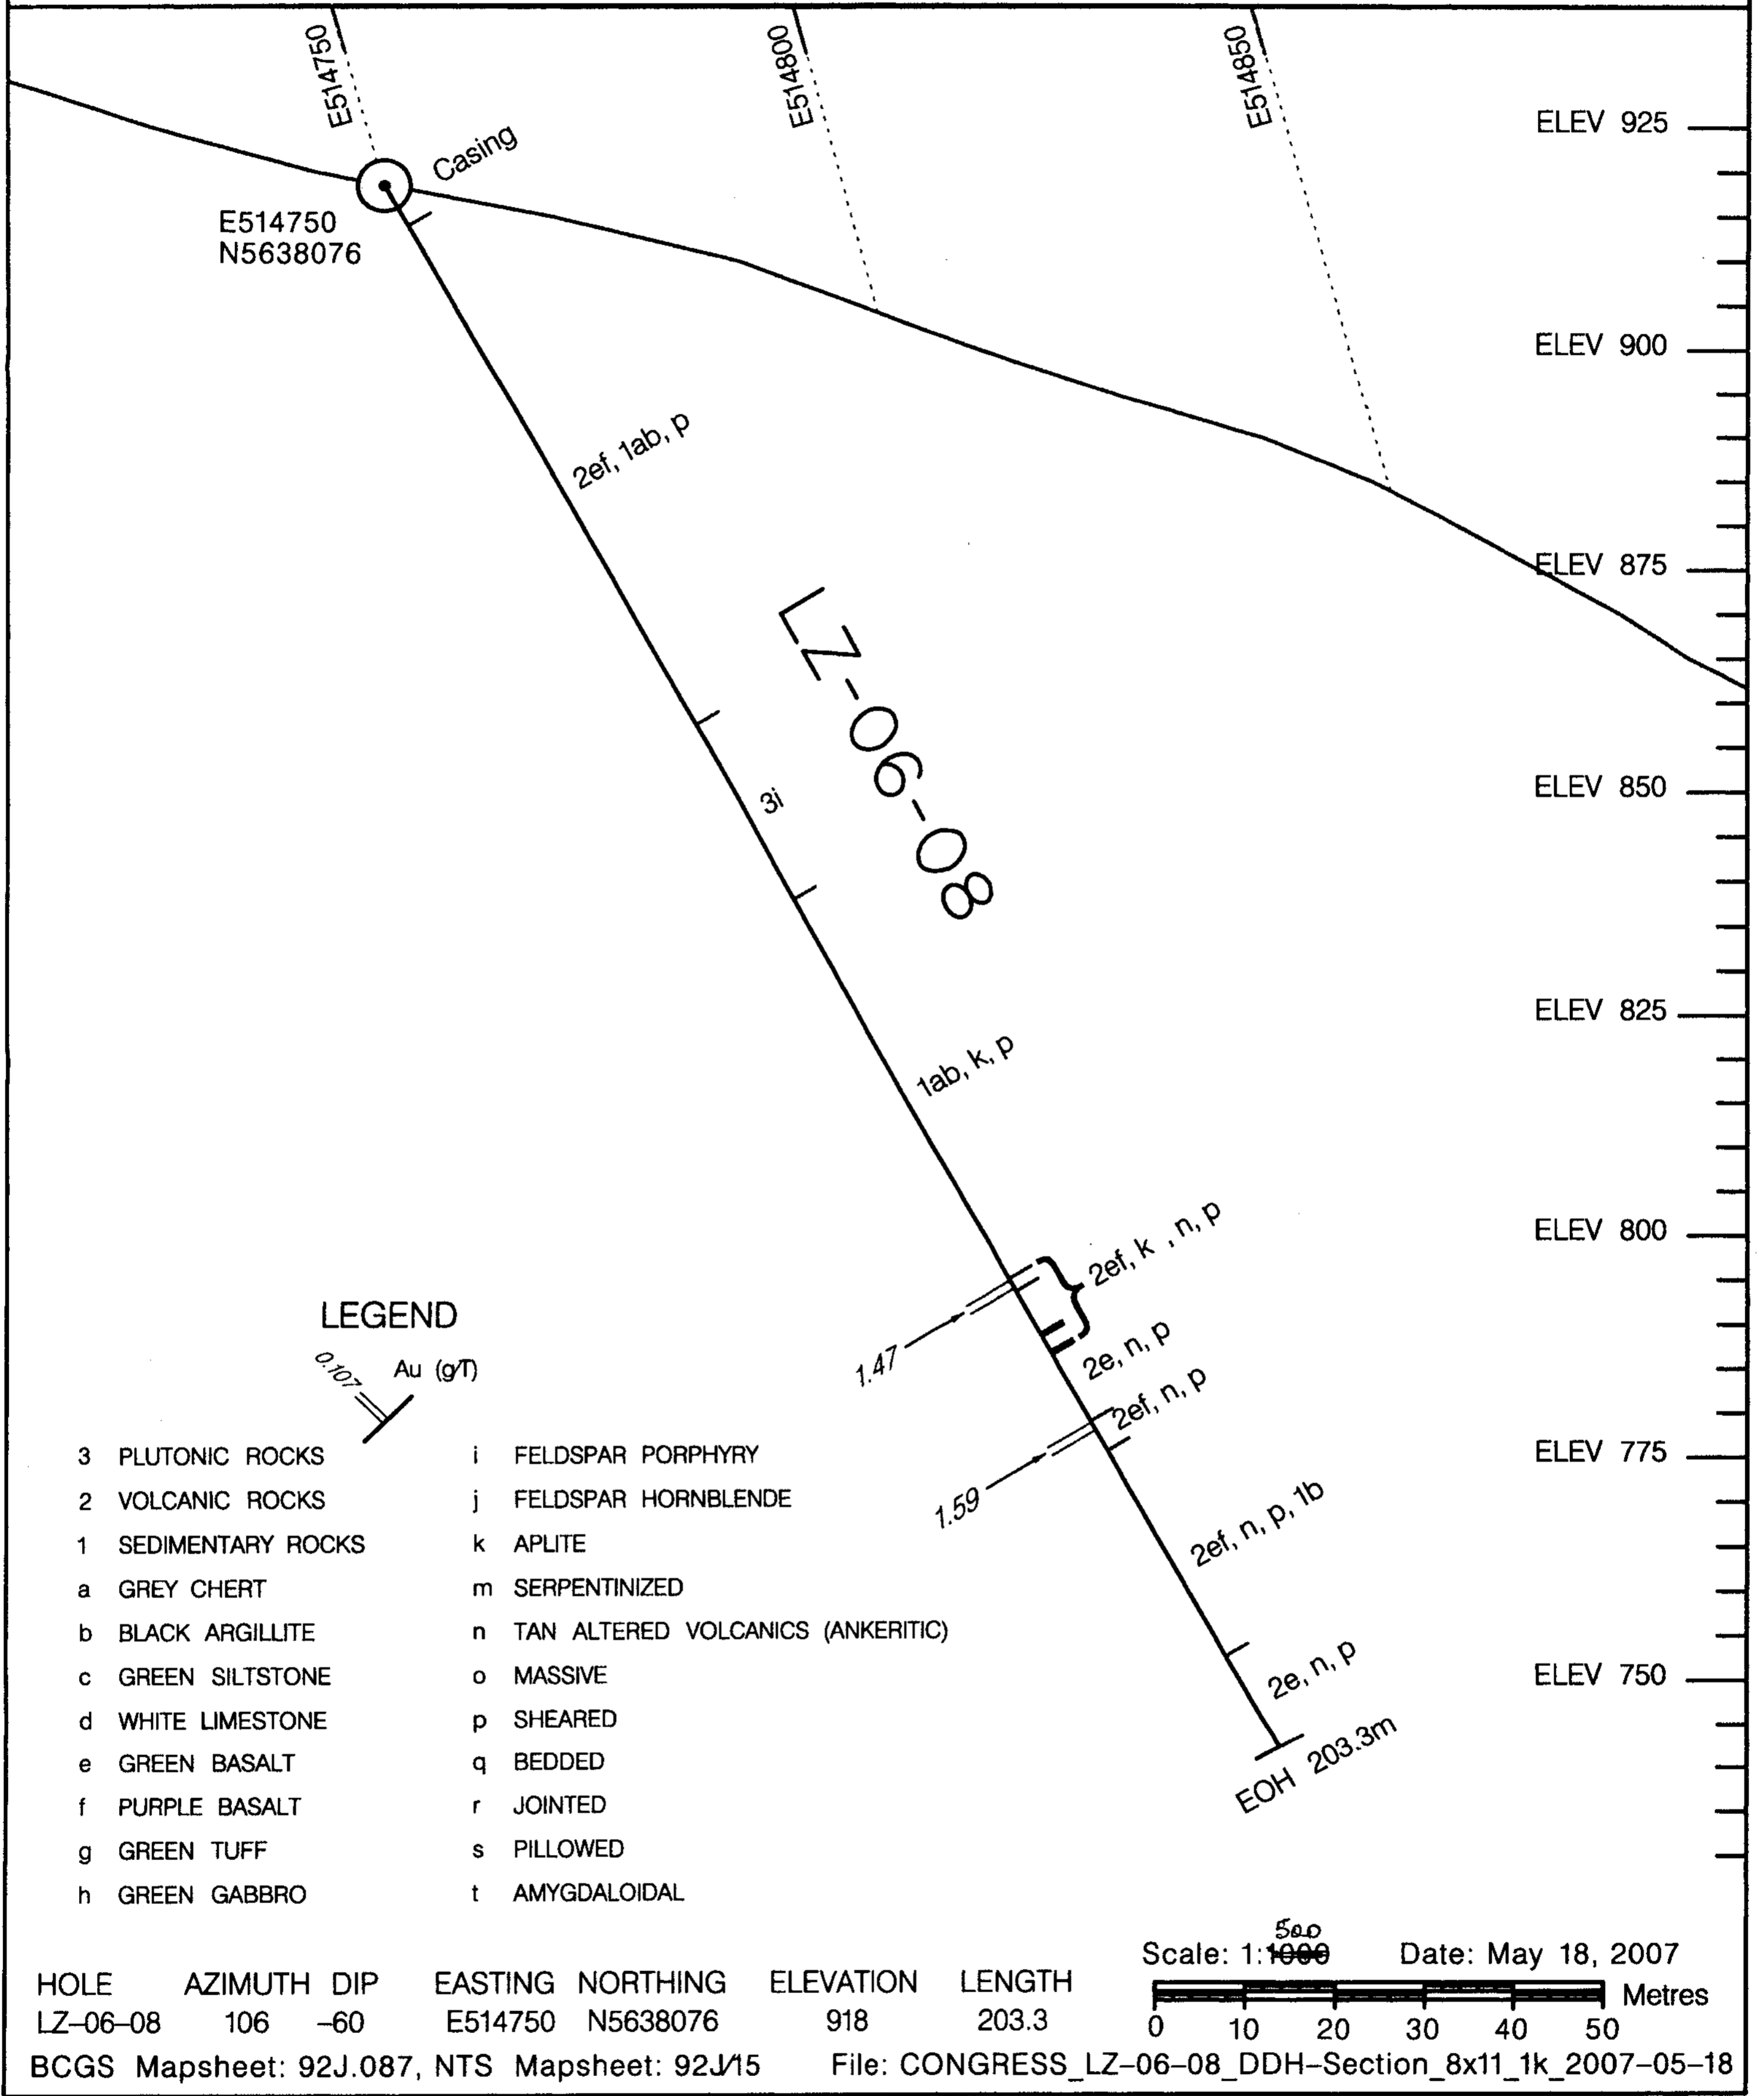



**CONGRESS PROPERTY - LOU ZONE**  
**DDH SECTION LZ-06-09**  
**LOOKING NORTH (10 Degrees)**

