

**Assessment Report on the 2007 Drill Program
on the Crack Moly Property
(Scuzzy Showing)
New Westminster Mining Division**

**BC Geological Survey
Assessment Report
29857**

NTS 92H/13W

Latitude 49° 52'N; Longitude 121° 49'W
NAD 83, UTM Zone 10

For:

PACIFIC CASCADE MINERALS INC.
520 – 700 West Pender Street
Vancouver, B.C.
V6C 1G8

Wesley Raven, P.Geol.

April 7, 2008

Table of Contents

TABLE OF CONTENTS	2
LIST OF TABLES	3
LIST OF FIGURES	3
LIST OF APPENDICES	3
SUMMARY.....	4
1. INTRODUCTION	5
2. LOCATION ACCESS AND TOPOGRAPHY	6
3. CLAIM STATUS	9
4. HISTORY.....	11
6. PROPERTY GEOLOGY.....	15
7. 2007 EXPLORATION PROGRAM.....	18
7.1 Drilling.....	18
General Parameters.....	18
7.2 General Geology and Mineralization.....	21
1 Granodiorite;	21
2 Breccia;	21
3. Quartz-Porphyry;	21
7.3 Drill Hole Descriptions.....	22
CM07-01 and 02 (Figures 6 and 7)	22
CM07-03 (Figure 8)	23
CM07-04 (Figure 9)	27
CM07-05 and 06 (Figure 10)	27
CM07-07 (Figure 11)	27
CM07-08 (Figure 12).....	27
CM07-09 (Figure 13).....	33
7.4 Drilling Summary	35
8. CONCLUSIONS AND RECOMMENDATIONS	36
9. STATEMENT OF QUALIFICATIONS	37
9.1 Wesley Raven.....	37
10. REFERENCES.....	38
12. STATEMENT OF COSTS.....	39

List of Tables

Table 1.	Crack Moly Property Claim Status.....	9
Table 2.	Crack Moly Project Drill Hole Information.....	20
Table 3.	2007 Drill Hole Intercepts.....	33

List of Figures

Figure 1.	Location Map	8
Figure 2.	Claim Map	10
Figure 3.	Regional Geology	14
Figure 4.	Property Geology – Scuzzy Showing	16
Figure 5.	Crack Moly Property – 2007 Drill Hole Plan	19
Figure 6.	Drill Section CM07-01	24
Figure 7.	Drill Section CM07-02	25
Figure 8.	Drill Section CMo7-03	26
Figure 9.	Drill Section CM07-04.....	28
Figure 10.	Drill Section CM07-05, 06.....	29
Figure 11.	Drill Section CM07-07	30
Figure 12.	Drill Section CM07-08.....	31
Figure 13.	Drill Section CM07-09.....	32

List of Appendices

Appendix 1.	Drill Logs.....	40
Appendix 2.	Assay Results.....	41

Summary

The Crack Moly property is comprised of eight contiguous mineral claims all of which are owned (100%) by Pacific Cascade Minerals Inc, in the New Westminster Mining Division. The property is centred at 49°52' North latitude and 121° 49' West longitude, on the east side of Harrison Lake, approximately 55 kilometres west-northwest of Hope, B.C., and 28 kilometres west from Boston Bar, B.C. Several Forest based communities within a 2-hour drive of the property can supply most materials, heavy equipment, and personnel for mining development in addition to basic exploration supplies.

The terrain is steep and rugged, with thick, dense west coast forest cover comprising cedar, hemlock, spruce and fir at the lower elevations. The tree cover fades with elevation to stunted shrubs and grasses to bare rock. The area of work is mainly bare rock in a cirque bowl.

The exploration program comprised nine diamond drill holes totaling 2,437.49 metres from seven setups. The program included camp construction, the first camp, referred to as the 'lower camp', was positioned too far down the mountain slope and was subsequently moved to a higher elevation. The program was conducted from July 1, 2007 to Dec. 28, 2007, with the bulk of the work done in August and September 2007, at a cost of \$996,228.90. Crews were weathered in by snowfall late in the program resulting in considerable standby time for both crews and equipment.

1. Introduction

The Crack Moly property is located approximately 28 kilometres southwest of Boston Bar, BC. The property covers a gossanous area within granodiorite and quartz monzonite, the Late Cretaceous Scuzzy Pluton and represents a porphyry molybdenum target. Within the gossan three mineralized zones have been identified, the Central Moly, Sericite Fracture and Quartz-Moly Breccia.

Molybdenum mineralization has been observed as coarse-grained rosettes along selvages of larger quartz veins, as disseminations in the selvages of quartz veinlets and lining the walls of cavities in some breccias. Historic rock sample assays from programs in the 1980's range from 0.004% Mo in pyrite rocks to 8.27% Mo from a 10 centimetre wide quartz vein. In addition a 50 centimetre sample across a rusty weathering zone assayed >0.1% tungsten, the source of the tungsten was not identified. Soil geochemical sampling outlined a large zone of greater than 20 ppm Mo measuring 1500 x 500 metres with peripheral anomalous W geochemical values. Fracture controlled molybdenite mineralization was observed within the geochemical anomaly.

In 2005 field crews under the direction of United Exploration Management Inc. completed line cutting, rock sampling and 3D-IP surveys on two grids, the Scuzzy grid (7.45 line-kilometres) and the Alt grid (7.6 line-kilometres). This work led to the planning and execution of the drill program described in this report.

2. Location Access and Topography

The Crack Moly property is centred on a north-south trending ridge line about five kilometres east of the north-south valley occupied by Big Silver Creek, which drains into Harrison Lake. The claims are centred at 49° 52' North latitude and 121° 49' west longitude on NTS map sheet 92H/13 (Figure 1). The nearest community is Boston Bar, B.C., approximately 28 kilometres to the east on Highway #1, the Trans-Canada Highway. Helicopter service from Hope (65 kilometres to the south) provides convenient access to the property on which landing sites are numerous. Helicopter access can also be gained from Boston Bar, however there is no helicopter base there.

Elevations on the property range from 760 metres (2,500') in the southeast portion of the claims to 1,950 metres (6,500') near the Scuzzy showing. The eastern, western and southern portions of the property are above timberline. The northern and central portions of the property lie on moderate to steep slopes that are forested with a variety of tree species. Local areas within the property are very steep and inaccessible.

Logging activity has created several road systems that pass within a few kilometres of the property, two of the roads actually enter the property boundaries. The Nahatlatch River logging road passes within 10 kilometres of the northern property boundary. To the east, along Kookipi Creek, recent logging activity provides a good road passing within the property at the south. As well, logging roads extend to the headwaters of Big Silver Creek in the valley hosting the Scuzzy showings. Roads here are within 1-2 kilometres of the showings. Both the Nahatlatch Main and Kookipi roads provide access to Boston Bar, approximately 30 kilometres by the road to the east. Boston Bar is serviced by Highway #1, and both the CN and CP railways.

Heavy equipment is available at any of the logging communities within 90 minutes drive of the property, principally Hope or Boston Bar. As well full services – police, hospitals, supplies, schools, restaurants and hotels are available. Vancouver, three hours drive west, has drilling and assay facilities.

Major power transmission lines are 20 kilometres east along Highway #1 and several river power-generating facilities have been built or are proposed within 30 kilometres of the

project area. Small creeks and lakes within the property are suitable to support exploration activities.



Figure 1. Location Map

3. Claim Status

The Crack Moly property is comprised of the SCH 1 to SCH 7 claims and the Scuzzy 1 claim, located in the New Westminster Mining Division. The claims are centred at 49° 52' North latitude and 121° 49' West longitude on NTS map sheet 92H/13 and are shown on Figure 2. All claims are registered (100%) to Pacific Cascade Minerals Inc. Claim details are shown in Table 1 and reflect assessment credits claimed from the 2007 drill program, the work for which is described in this report.

Table 1. Crack Moly Property Claim Status

Tenure #	Claim Name	Date Registered	Expiry Date	Area (ha)	Registered Owner
518498	SCH 1	July 28/05	Jan. 12, 2013	375.316	Pacific Cascade Minerals
518507	SCH 2	July 28/05	Jan. 12, 2013	336.626	Pacific Cascade Minerals
518508	SCH 3	July 28/05	Jan. 12, 2013	521.085	Pacific Cascade Minerals
518510	SCH 4	July 28/05	Jan. 12, 2013	521.128	Pacific Cascade Minerals
518512	SCH 5	July 29/05	Jan. 12, 2013	521.198	Pacific Cascade Minerals
518513	SCH 6	July 29/05	Jan. 12, 2013	520.92	Pacific Cascade Minerals
518514	SCH 7	July 29/05	Jan. 12, 2013	520.98	Pacific Cascade Minerals
501386	Scuzzy 1	Jan 12/05	Jan. 12, 2013	521.079	Pacific Cascade Minerals
8 claims				3338.332	

In British Columbia mineral claim assessment requirements are \$4.00 of work per hectare per year, or cash in lieu, plus \$0.40 filing fees per hectare per year for the first three years, thereafter rising to \$8.00 of work per hectare per year plus \$0.40 filing fees per hectare per year.

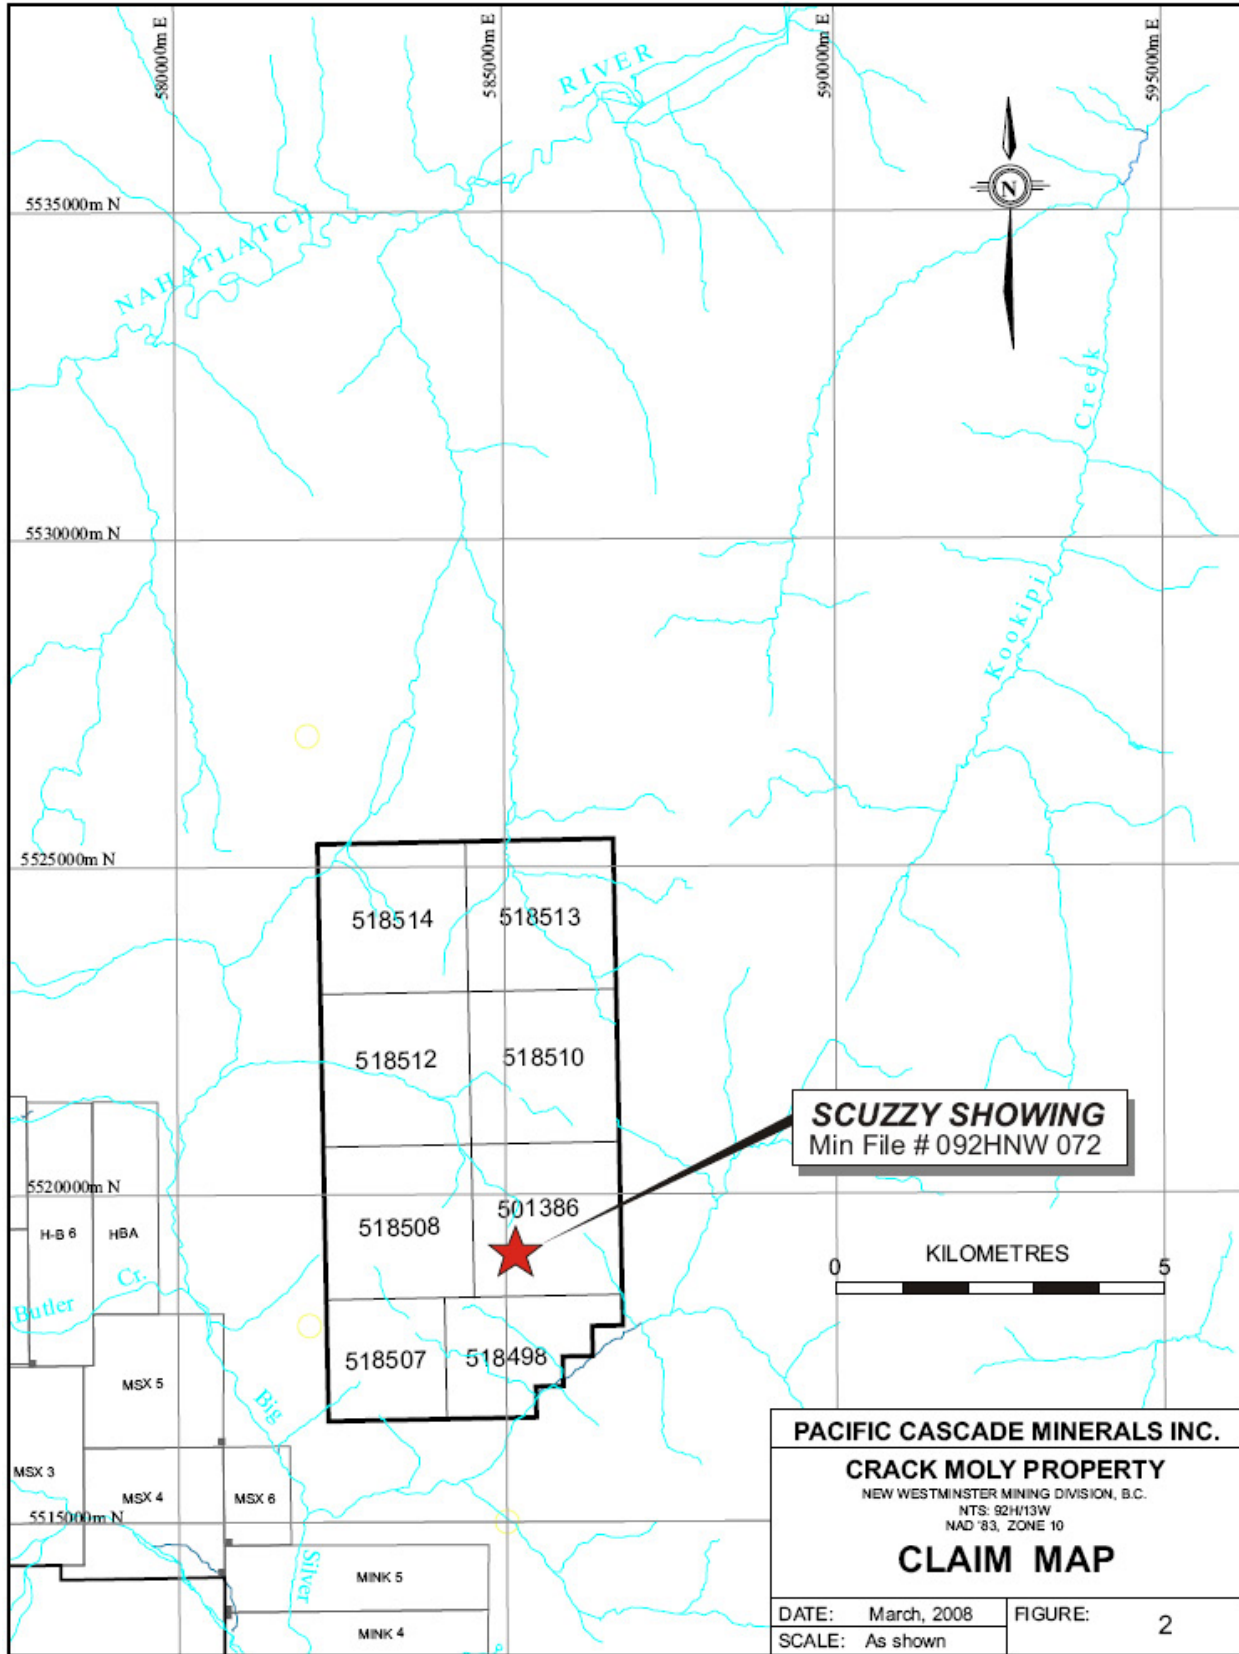


Figure 2. Claim Map

4. History

The area was first recognized in August 1980 when molybdenite was discovered in a float sample at the headwaters of Big Silver Creek. Follow-up prospecting discovered molybdenite-bearing quartz veins in an area of strong gossan staining. The area was staked and work commenced in September of the following year, 1981. From 1981 to 1984 the property was worked on by JMT Services Corp.

In the 1981 program JMT Services Corp. undertook a preliminary mapping and rock chip-sampling program on two claims, which covered the gossanous ridge. A total of 157 rock chip samples were collected and analysed for Cu, Mo, Pb, Zn, W and F. Contouring of the rock sample data showed the 5 ppm Mo contour corresponded closely to the outer limit of quartz veining. The >20 ppm Mo contour defined an area measuring about 1,500 metres x 500 metres lying within the breccia complex. Molybdenum values ranged from 1 to >250 ppm, visible molybdenite was observed in some rock samples. Tungsten data outlined anomalous zones outward from the molybdenum zone and were roughly centred on the northwest boundary of the breccia complex. Values ranged from 1 to 750 ppm tungsten. An east-west trending copper anomaly (>20 ppm Cu) flanks the southern margin of the breccia complex with a north-trending lobe on the west side of the breccia complex. Copper values ranged from 1-3,300 ppm with chalcopyrite observed in hand samples. Zinc values outlined an anomalous area (>50 ppm) centred on the north-central border of the breccia complex. Zinc values ranged from 1-3,200 ppm zinc.

A limited program (3 days) was completed in September 1982. This work included mainly a study of fracture patterns on an enlarged air photo of the claims and study of the intensity of mineralization within the molybdenum rock geochemical anomaly. This was achieved by comparing air photo linears with the mineralized fractures seen in the field. In addition seven rock chip samples were collected from molybdenite-bearing veins and assayed for base and precious metals content. Molybdenum values ranged from 0.004% to a high of 8.27%, the latter from a 10 centimetre wide quartz-molybdenite vein. Tungsten values ranged from 5 to >1,000 ppm, the latter a 0.5 metre chip sample across a rusty weathering zone; no significant precious metals assays were returned.

The objective of the 1984 program was to test previously collected rock samples for precious metals and additional elements to aid in spotting drill holes. A total of 150 rock chip sample pulps were analysed for Au, Ag, Co and Ni by US Borax Research Corp., USA.

Only silver produced a contourable pattern, a few samples were anomalous in gold and generally correspond to the highest silver assays. Cobalt and nickel were quite flat. Silver values ranged from 0.2 ppm to 32.4 ppm, only three samples returned gold assays exceeding analytical detection limits, those sampled ranged from 0.05 ppm to 0.18 ppm. The ≥ 1.0 ppm silver contour flanks the south and west margins of the ≥ 20 ppm molybdenum contour. A smaller area of ≥ 1.0 ppm silver lies on the northeast portion of the breccia complex. Of interest were the two highest silver assays, 32.4 and 6.3 ppm occur near the 050° trending sericite fracture zones.

In 2005 field crews under the direction of United Exploration Management Inc. completed physical work (camp building, grid establishment), geochemical (rock sampling) and geophysical (IP) surveys on the Crack Moly project. The work was completed on two grids, the Scuzzy grid and the Alt grid. At the Scuzzy grid surveys included grid establishment, (7.45 line-kilometres), geochemical, (133 rock samples) and a 3D IP survey (7.45 line-kilometres). At the Alt grid surveys included grid establishment (7.6 line-kilometres) and a 3D IP survey (7.6 line-kilometres). No rock samples were collected from the Alt grid.

5. Regional Geology

The property is situated near the axis of the Cascade Range which is underlain by broad areas of granitoid intrusions: the Spuzzum and Scuzzy Plutons, flanked on the west by pen-
dants of Custer gneiss and dark pelitic schists of probable Paleozoic age, and on the east by
meta-sediments of possible Triassic age (Figure 3). The Spuzzum Pluton is dated at 74 My.
and the Scuzzy Pluton at 70 M.y. Younger (Late Tertiary) intrusions are known in the Hope
area – 18 M.y. and a number of early Tertiary volcanic centres exist north of the prospect.

Numerous molybdenite occurrences are present in an arcuate pattern following the central
axis of the Cascade Range, and include AM breccia 40 kilometres southeast of Hope, the
“Pipe” prospect on Sawmill Creek near Yale, the “Gem” deposit on Clear Creek, 28 kilome-
tres south of the claims, the Cataract deposits 35 kilometres northwest, and several other
occurrences extending north-westward to Salal Creek, 150 kilometres northwest.

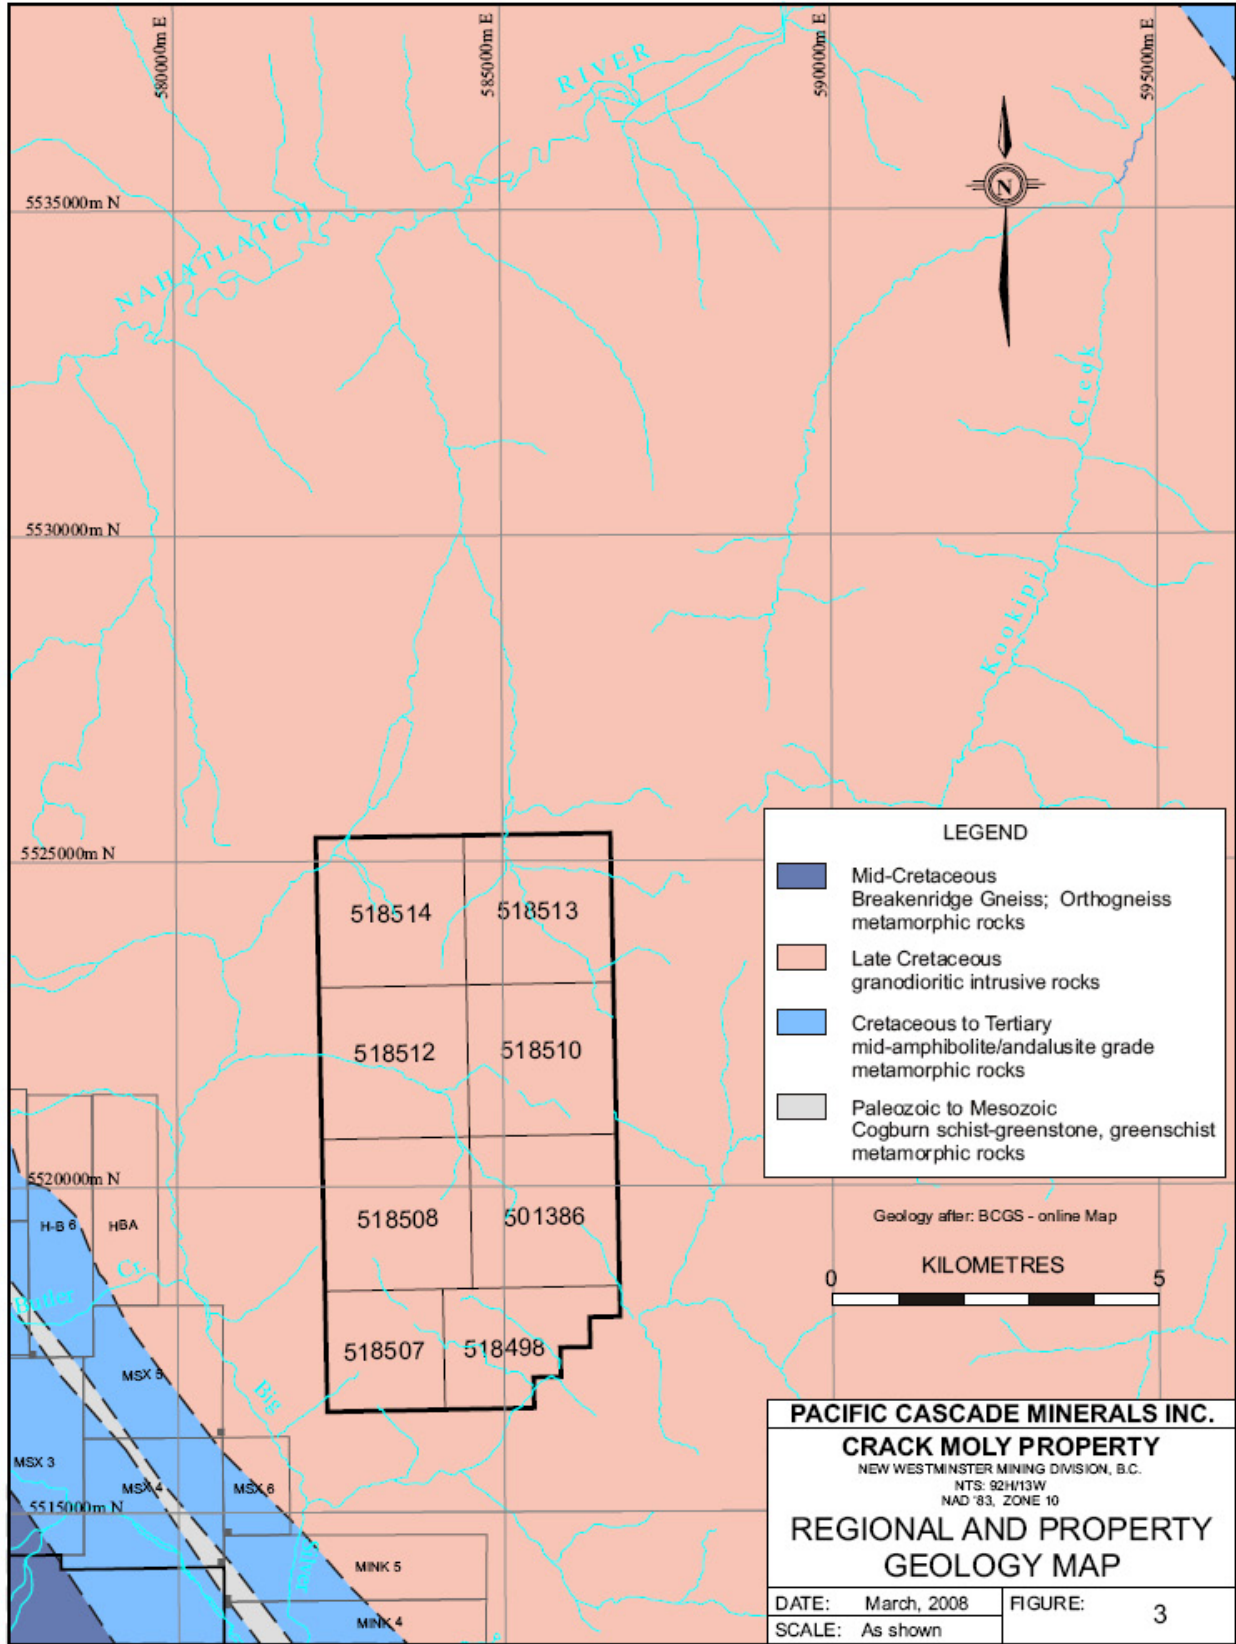


Figure 3. Regional Geology

6. Property Geology

The Scuzzy showing covers a rusty, weakly altered and mineralized phase of the Scuzzy Pluton; the subtle gossan stands out well against the uniform grey barren appearance of the large plutonic mass. Detailed geology of the showing is shown on Figure 4.

The barren country rock is medium grained, quartz-rich granitoid – probably a granite or quartz monzonite, with approximately 5% mafics (biotite exceeds hornblende) and abundant subhedral quartz phenocrysts. Minor but noticeable muscovite is present.

Traversing across the Scuzzy showing the first noticeable change in the rock is rusty coloration. At this point no mineralogical or textural difference exists. Continuing into the zone, the rock becomes slightly pyritized and mafics are destroyed, giving the rock a leucocratic appearance. Zones of silicification occur where clay alteration is noticeable as greenish colouration and quartz veins are common. Chloritic alteration is present where mafics are still present. In the centre of the zone of interest a prominent dark coloured feldspar porphyry dyke occurs. This forms a sharp rusty coloured ridge that forms the western limit of a small cirque. Another elongate section of the dyke is seen in the south-central area of the cirque, and a prominent lineation trending northeastward through the cirque probably has offset the dyke by several hundred metres. The dyke contains fresh biotite, pyrite and has quartz veins (barren) and inclusions of quartz monzonite. The rock may be a variety of lamprophyre and is thought to be pre-mineral.

The fault zone mentioned previously is marked by a topographic depression trending northeastward and cuts off the western limb of the lamprophyre dyke. The fault zone contains a quartz vein 30 centimetres wide. South of the fault, alteration is stronger and the rock is slightly coarser-grained.

The best mineralization is present within the cirque area and may be related to the intersection of the dyke and the fault. The south limit of alteration and mineralization is marked by the northeast trending ridge that forms the south wall of the cirque. The actual zone of interest is roughly 600 metres in diameter.

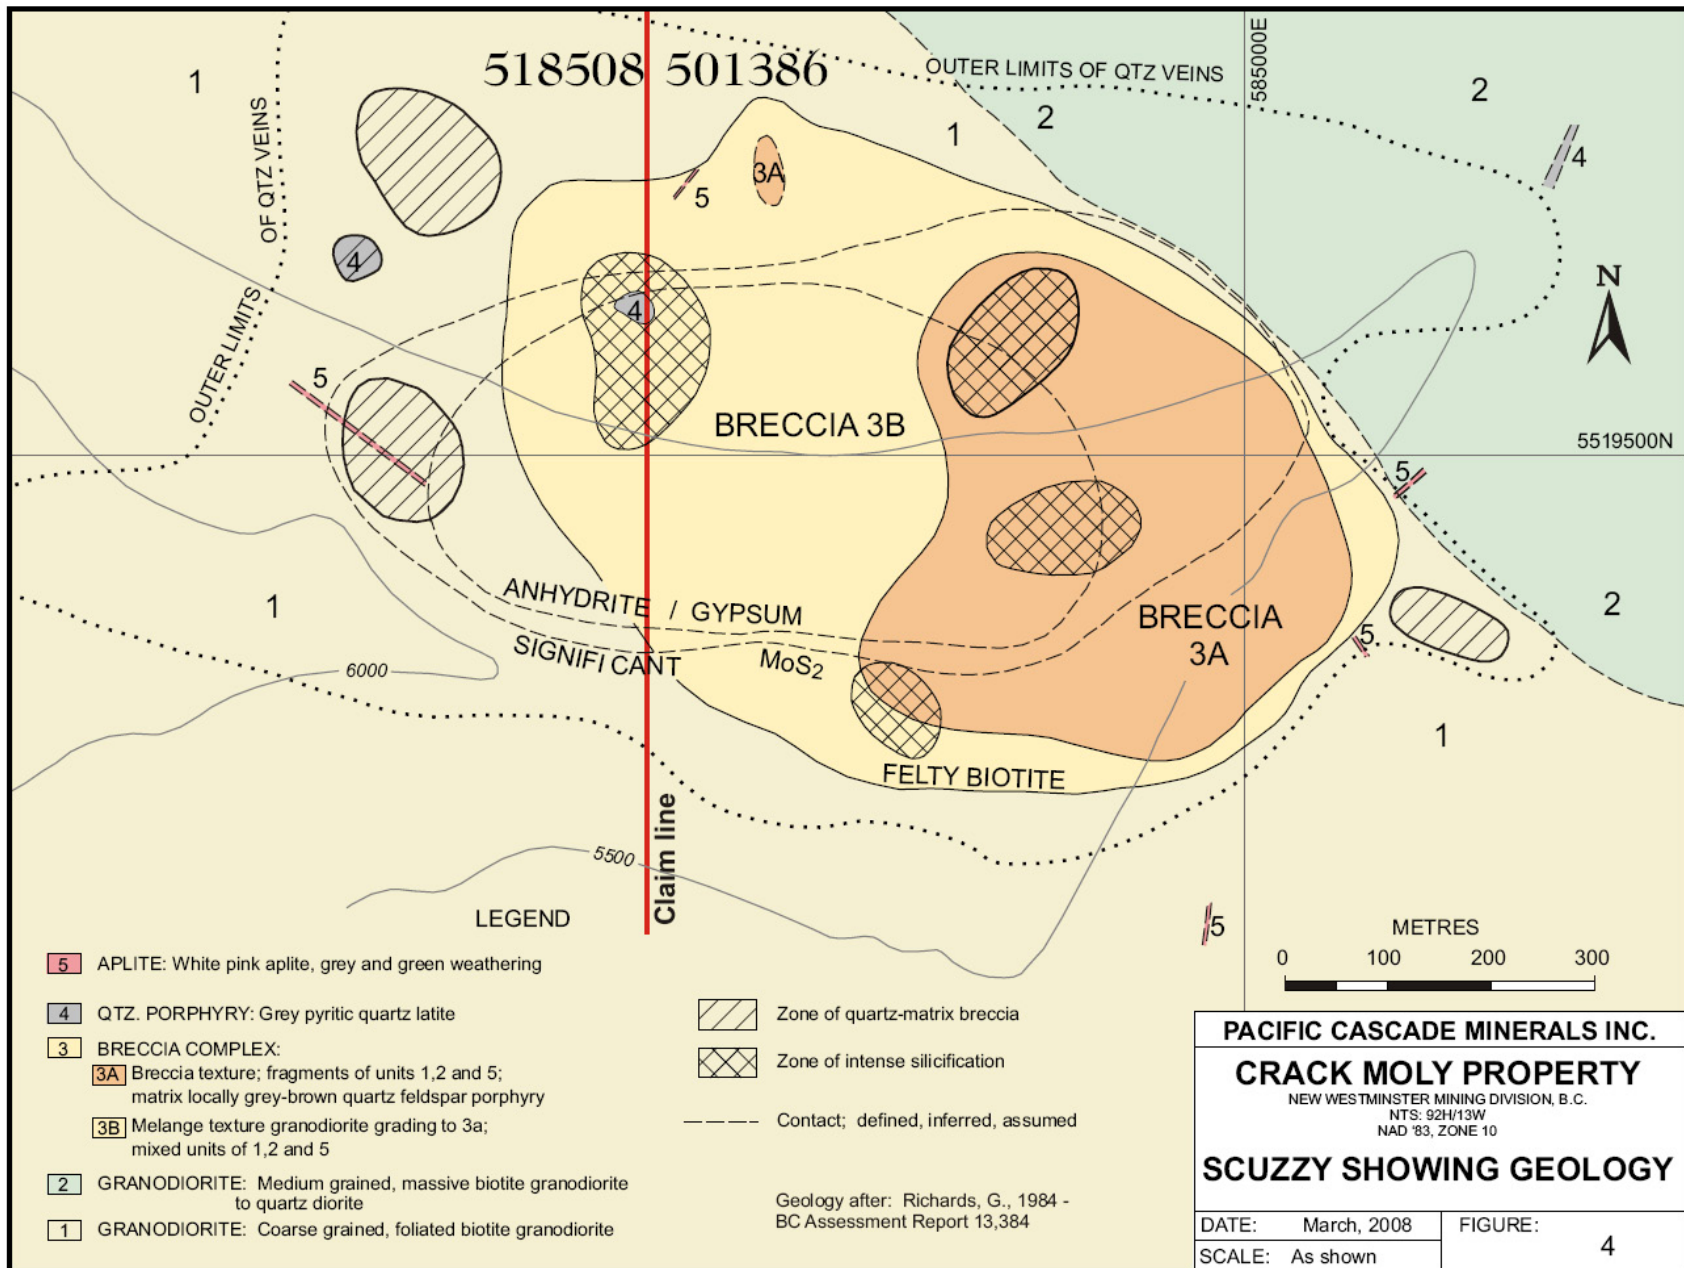


Figure 4. Property Geology – Scuzzy Showing

The molybdenite and very sparse chalcopyrite mineralization is confined to quartz veins and siliceous zones and is mostly fine-grained. Nowhere is the mineralization particularly abundant. Nevertheless, molybdenite is scattered over the altered and rusty zone and this covers a significant area that is worthy of further exploration.

Past mapping programs have outlined three zones within the area of interest. These zones are named the Central Moly Zone, the Sericite Fracture zone, and the Quartz-Moly Breccia zone.

At the Central Moly Zone fracture controlled molybdenite is the predominant sulphide although minor pyrite, chalcopyrite and pyrrhotite are associated. The molybdenite occurs in spectacular coarse-grained rosettes along the selvages of the large quartz veins as much as 10 centimetres in width. Finer grained platy and disseminated molybdenite occur on the selvages of narrow quartz stringers, ribbon quartz veins, and along the walls of the interstitial cavities in some breccias, occasionally forming thick blebs of solid molybdenite. Molybdenite also occurs with other sulphides as fine coatings along tight fractures. Conspicuous molybdenite is restricted to approximately the innermost 200 metre central core of the molybdenite zone. Outwards, molybdenite becomes harder to detect visually.

In the Sericite Fracture Zone about ten very prominent fractures occur along the cliff face. They trend 050°, are spaced about 10 metres apart, and contain abundant coarse sericite in zones approximately one-half metre wide with quartz veinlets containing pyrite, molybdenite and chalcopyrite. In the field they extended at least 200 metres southwest where they disappeared over the ridgeline. To the northeast they continue some distance.

The Quartz-Moly Breccia Zone is a brecciated intrusive unit comprised of a quartz matrix breccia containing occasional blebs of coarse molybdenite up to 10 centimetres wide but generally two to four centimetres across. The molybdenite occasionally has minor associated pyrite and heavy Mn staining. Otherwise the quartz is white and free of other minerals. The breccia fragments are angular and measure one-half to five metres in maximum dimension often displaying only minor rotation.

7. 2007 Exploration Program

7.1 DRILLING

General Parameters

A drill program was initiated on the Crack Moly program to test both surface mineralization and IP chargeability and resistivity targets at depth. Drill pad construction was completed by ISE Blasting Ltd of North Vancouver, B.C., who constructed pads from a combination of 6"x6" and 8"x8" timbers for cribbing with 2"x10" decking. Some blasting was required for pad construction and anchor bolts were placed at key points around the setup to anchor to drill to. Drill site reclamation was also done by ISE Blasting with two of seven pads reclaimed in 2007, the balance to be finished in 2008. The drill contract was awarded to Westcore Drilling of Hope, B.C. The program was completed with an Atlas Copco 250 helicopter portable diamond drill, core size was BQTK (equivalent to B-thinwall). Nine holes totaling 2,437.49 metres were completed from seven setups (Figure 5). The actual drilling portion of the program commenced on August 9, 2007 with the casing of hole CM07-01 and finished on September 23, 2007. Drill hole collar information is shown in Table 2, Crack Moly Project Drill Hole Information. UTM coordinates are NAD 83, Zone 10. Collar locations were derived by handheld GPS until an accuracy of +/- 3 metres was attained. The core is stored on site, with holes CM07-01 to 03 at the lower camp and holes CM07-04 to 09 at the upper camp.

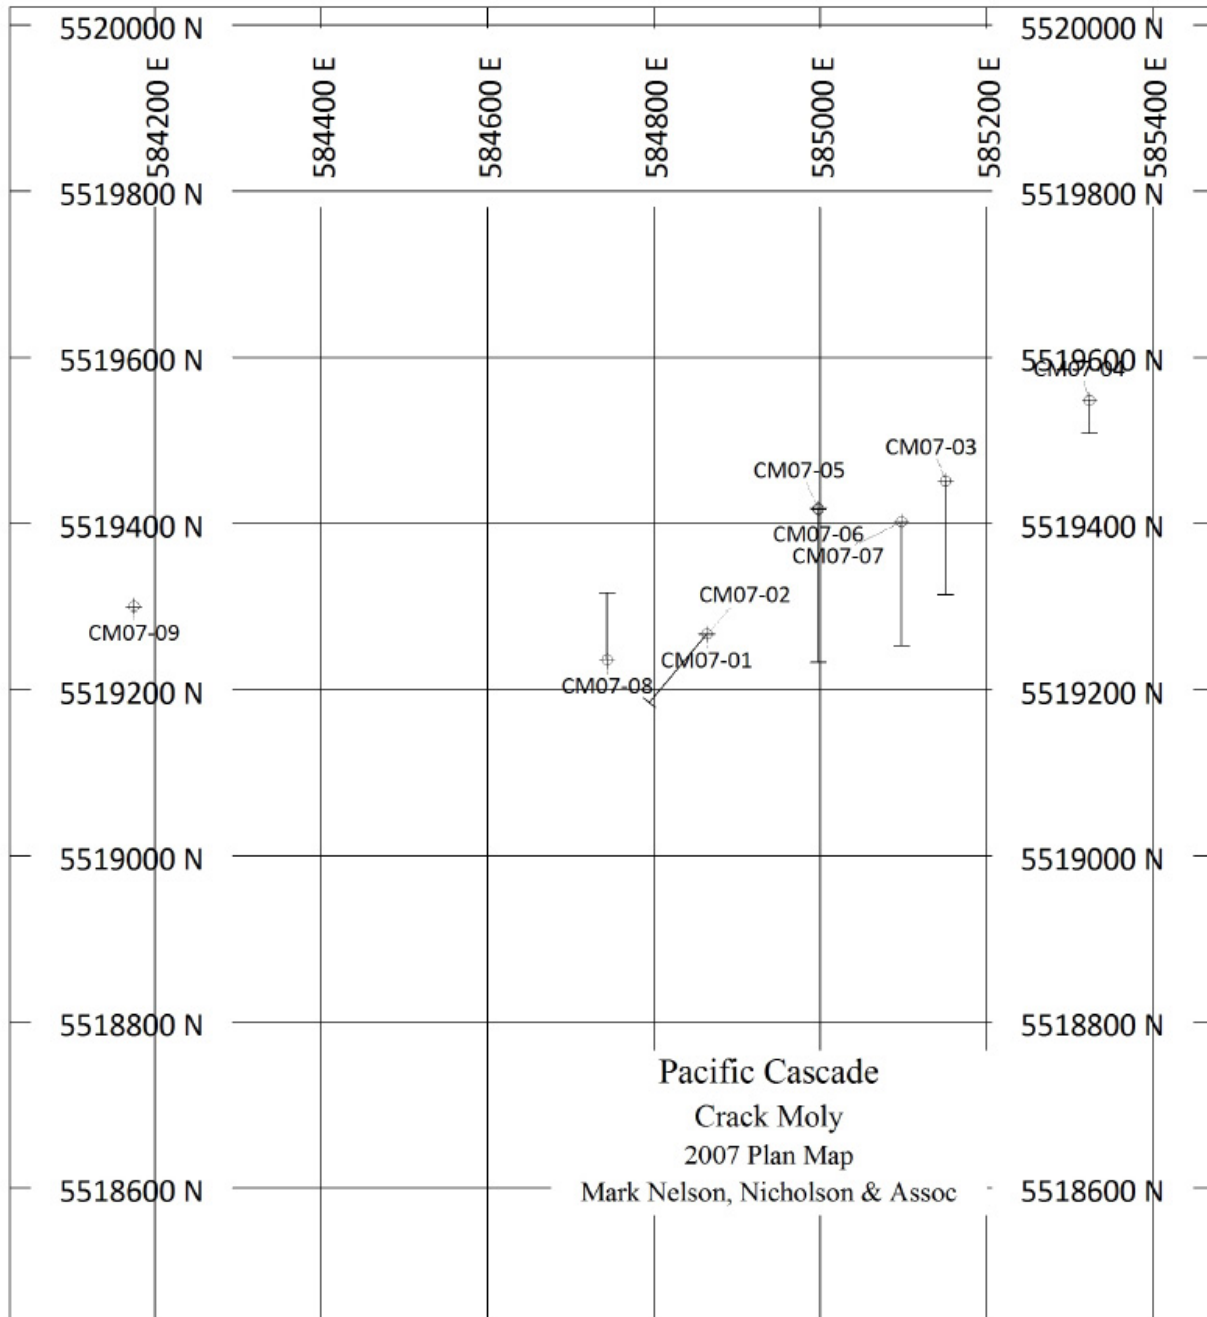


Figure 5. Crack Moly Property – 2007 Drill Hole Plan

Table 2. Crack Moly Project Drill Hole Information

Hole #	Site Number	Easting	Northing	Elevation (metres)	Az	Dip	Length (metres)	Cumulative Length (m)
CM07-01	H	584864	5519267	1749	N/A	-90	343.51	343.51
CM07-02	H	584864	5519267	1749	220	-65	255.12	598.63
CM07-03	L	585151	5519451	1681	180	-65	323.70	922.33
CM07-04	N	585324	5519548	1658	180	-70	114.91	1037.24
CM07-05	J	584998	5519417	1677	180	-55	320.95	1358.19
CM07-06	J	584998	5519418	1677	N/A	-90	212.14	1570.33
CM07-07	X	585098	5519402	1693	180	-60	297.18	1867.51
CM07-08	G	584745	5519236	1768	360	-76	331.93	2199.44
CM07-09	P	584675	5519279	1788	N/A	-90	238.05	2437.49

Sample intervals were selected by the onsite geologists and generally ranged from 1.0 to 3.0 metres depending upon lithology and mineralization. All core submitted for analysis was sawn in half with a diamond saw, placed into a 12"x20" plastic sample bag with an assay tag number from the lab and the same number written on the outside of the bag with black felt maker, and the bag sealed with a "zap" strap. An analytical molybdenum standard purchased from CDN Resource Laboratories Ltd., Delta, B.C., was randomly inserted into the sample sequence with several standards per hole. A blank was used on occasion but it was not a true analytical blank and the practice was discontinued when several samples selected as a blank returned appreciable molybdenum. Samples were shipped from camp on a hole-by-hole basis to Valley Helicopters operations base in Hope, B.C., and from there transported by Greyhound bus to Eco Tech Laboratory Ltd. in Kamloops, B.C. All samples were subject to a 29- element ICP analysis (method BICP-12), for Mo exceeding 500 ppm a more precise assay method was employed (BOGA-27) and the results expressed in percent. The molybdenum assays reported in this report are for Mo, not MoS₂.

7.2 GENERAL GEOLOGY AND MINERALIZATION

The drill holes all encountered similar lithologies over varying lengths, the age relationships of the various units described below is uncertain. The lithologies are classified into three general categories:

1 Granodiorite;

1.1: Unaltered-coarse grained, massive granodiorite;

1.2: Weakly foliated-coarse grained granodiorite with weak foliation defined by biotite flakes;

1.3: Altered granodiorite through fine-grained infiltration of granitic rock. May contain molybdenite rosettes and crystals and plates and chalcopyrite crystals;

2 Breccia;

2.1: Monolithic breccia consisting of granodiorite angular inclusions in a finer-grained groundmass. Molybdenite is associated with quartz veinlets cutting or filling spaces;

2.2: Heterolithic breccia (melange) consists of angular fragments of granodiorite, quartz-porphyry, and absorbed granitic “clasts.” Molybdenite in fractures, quartz veins and in quartz-porphyry fragments;

3. Quartz-Porphyry;

3.1: Unaltered; very much aplitic in texture, white to light grey to very pale green colour. Aphanitic with porphyritic feldspar crystals, contains pyrite and chalcopyrite. Very quartz-rich and competent;

3.2: Red stain altered; this is a penetrating alteration that often has a alteration envelope surrounding it with a dark grey to black colouration. The alteration tends to follow fractures and then penetrates beyond the walls of the fractures into the rock. Molybdenite does not appear to be associated with the alteration;

3.3: Fractured quartz-porphyry, may be altered or not. The fractures are very fine to 20 centimetres in width, are quartz filled and contain very fine-grained molybdenite and chal-

copyrite, though rarely together. Coarser molybdenite rosettes can be seen but usually in larger quartz filled cracks;

The molybdenite mineralization is classified into three styles as follows:

1: - As coarse rosettes within vuggy quartz veins that have well developed quartz crystals. These are found within the breccias and altered granites.

2: - As well developed grains within the quartz porphyry and proximal to quartz veins in any material and also as interstitial material in the breccia units.

3: - Fine-grained molybdenite within veinlets that cut through all lithologies. These veins are from sub-millimeter to up to centimetre width and also may contain chalcopyrite within a quartz matrix. These cut the core at various angles and are the most common form of molybdenite mineralization.

Alteration in the intrusive body drill tested is relatively minimal and is comprised chiefly of biotite, sericite and silica. Biotite is the most abundant and is common in the granodiorite and biotite-hornblende granodiorite. Silicification is commonly present in the quartz porphyry and this same unit exhibits minor sericite as well.

7.3 DRILL HOLE DESCRIPTIONS



CM07-01 and 02 (Figures 6 and 7)

These holes were collared at the same setup, hole CM07-01 testing a chargeability high and CM07-02 testing a resistivity high. Hole CM07-01 collared in granodiorite, then an intermixed succession of heterolithic breccia, quartz porphyry, granodiorite and hornblende-biotite granodiorite, ending in mainly granodiorite and hornblende-biotite granodiorite. Hole CM07-02 also collared in granodiorite, then a thicker succession of intermixed mono- and heterolithic breccias, granodiorite, and minor quartz porphyry and ended in granodiorite. Molybdenite was scattered throughout both holes but was strongest in hole CM07-01, particularly in the lower portion of the hole where the interval from 187.41 to 343.51 metres averaged 0.035% molybdenum over 156.10 metres. In hole CM07-02 molybdenite was more concentrated in the upper portion of the hole with the interval 25.70 to 32.84 metres aver-

aging 0.037% molybdenum over 7.14 metres with scattered anomalous results over narrow intervals down to 130.15 metres.

CM07-03 (Figure 8)

This hole was collared to test the eastern flank of a chargeability zone at depth with associated moderate resistivity. The hole intersected a thick succession of granodiorite and hornblende-biotite granodiorite with intercalated sections of quartz porphyry; no breccia units were logged. The hole had molybdenite mineralization throughout the hole and was one of the best holes of the program, assaying 0.042% molybdenum over 233.25 metres from 1.25 to 234.5 metres. Within this section the interval from 140.22 to 155.63 metres assayed 0.216% molybdenum over 15.41 metres.

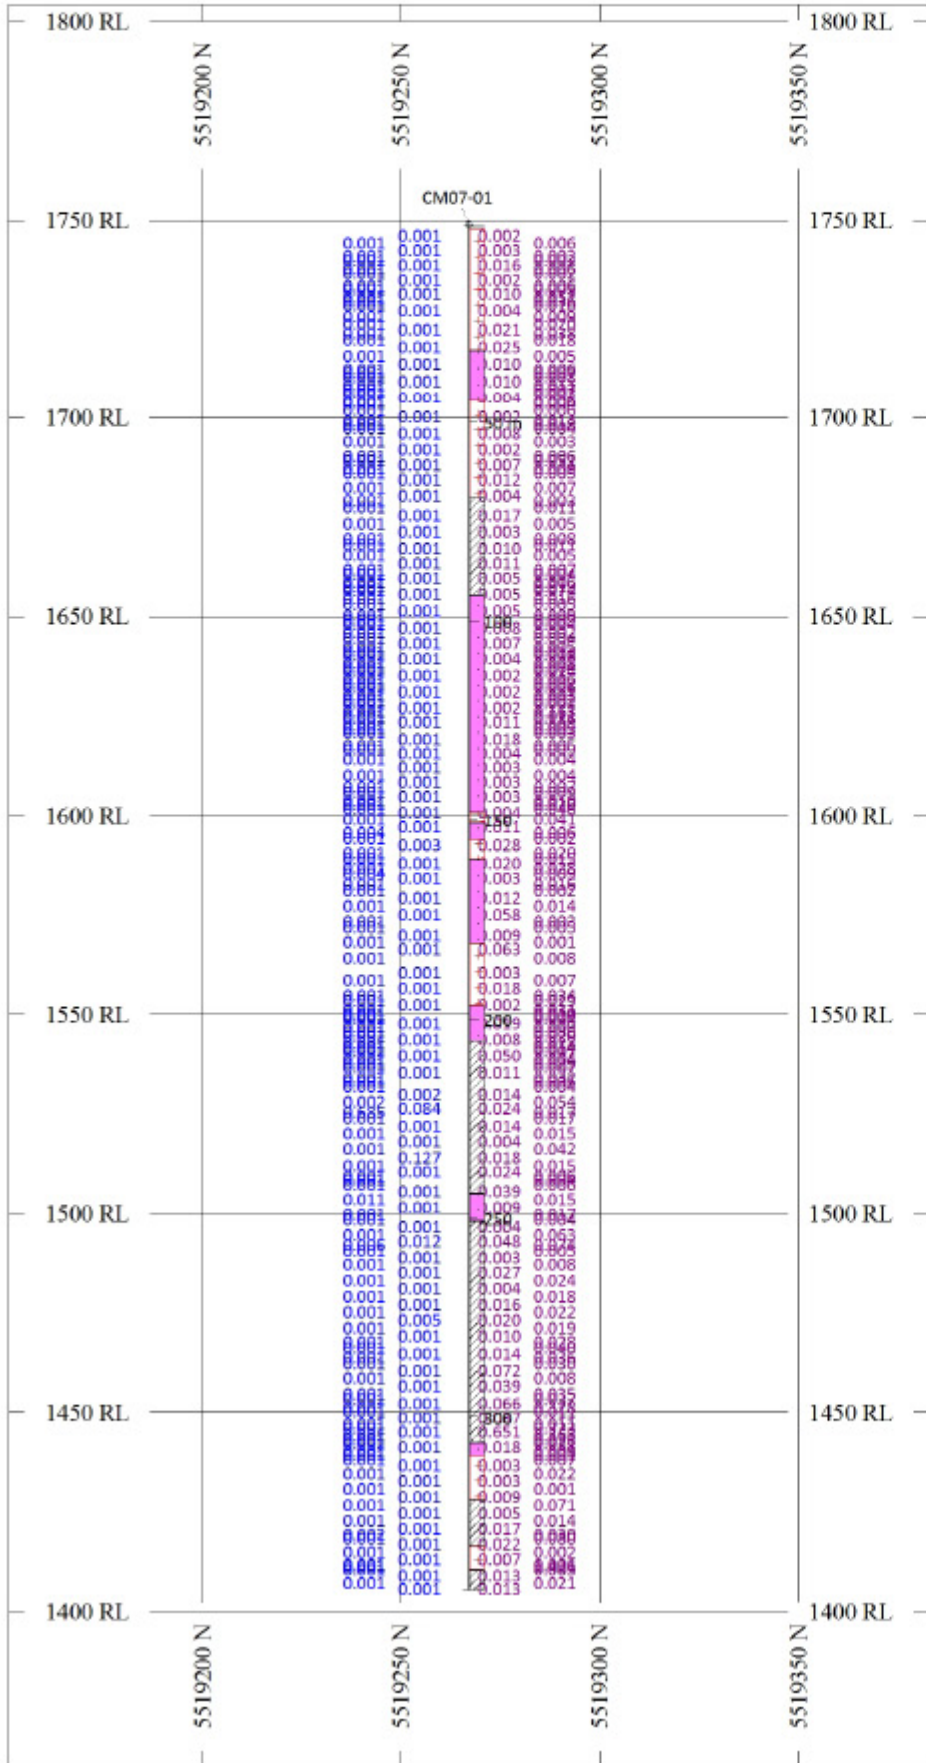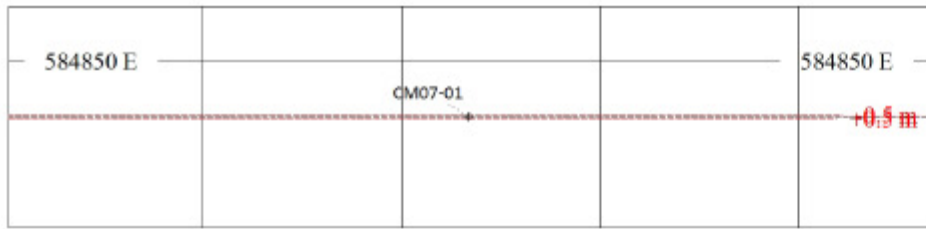

HOLES PLOTTED

TOTAL 1
CM07-01

ROCK CODES	L/R	PAT	LABEL	DESCRIPTION
Lithocode	R		BX	breccia
			NC	no core
			GD	granodiorite
			QP	quartz-porphry

ASSAYS	L/R	TEXT
Mo_pet	R	-----
W_pet	L	-----

SECTION SPECS:

REF. PT. E, N	584864 m	5519267 m
EXTENTS	231.8 m	443.4 m
SECTION TOP, BOT	1804 m	1361 m
TOLERANCE +/-	0.5 m	

SCALE 1 : 2000



(m)

*unknown

AZIMUTH = 0°

Pacific Cascade
Crack Moly
CM07-01
Mark Nelson, Nicolson & Assoc

Figure 6. Drill Section CM07-01

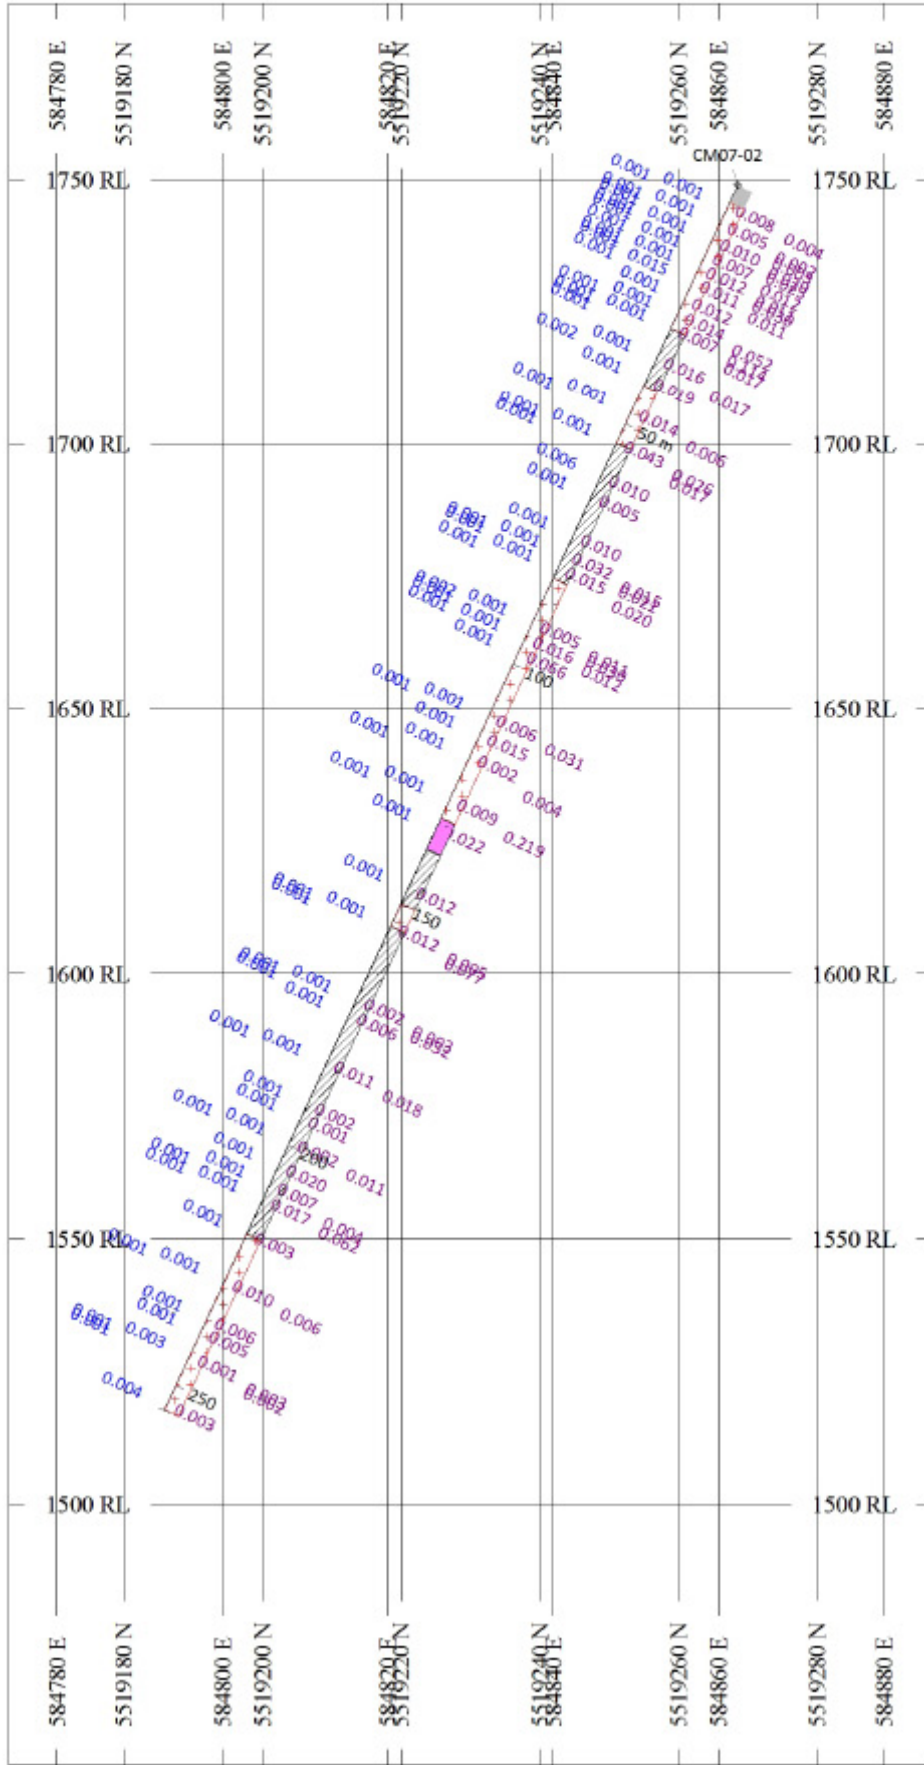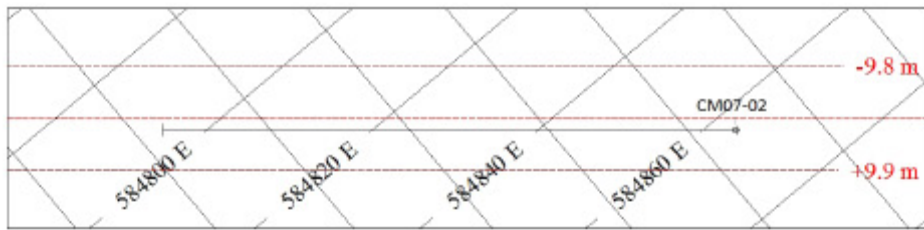

HOLES PLOTTED

TOTAL 1

CM07-02

ROCK CODES	L/R	PAT	LABEL	DESCRIPTION
Lithocode	R		BX	breccia
			NC	no core
			GD	granodiorite
			QP	quartz-porphyry

ASSAYS	L/R	TEXT
Mo_pet	R	-----
W_pet	L	-----

SECTION SPECS:

REF. PT. E, N	584830 m	5519230 m
EXTENTS	173.9 m	332.5 m
SECTION TOP, BOT	1783 m	1451 m
TOLERANCE +/-	9.85 m	

SCALE 1 : 1500


(m)

*unknown

AZIMUTH = 40°

**Pacific Cascade
Crack Moly
CM07-02
Mark Nelson, Nicolson & Assoc**

Figure 7. Drill Section CM07-02

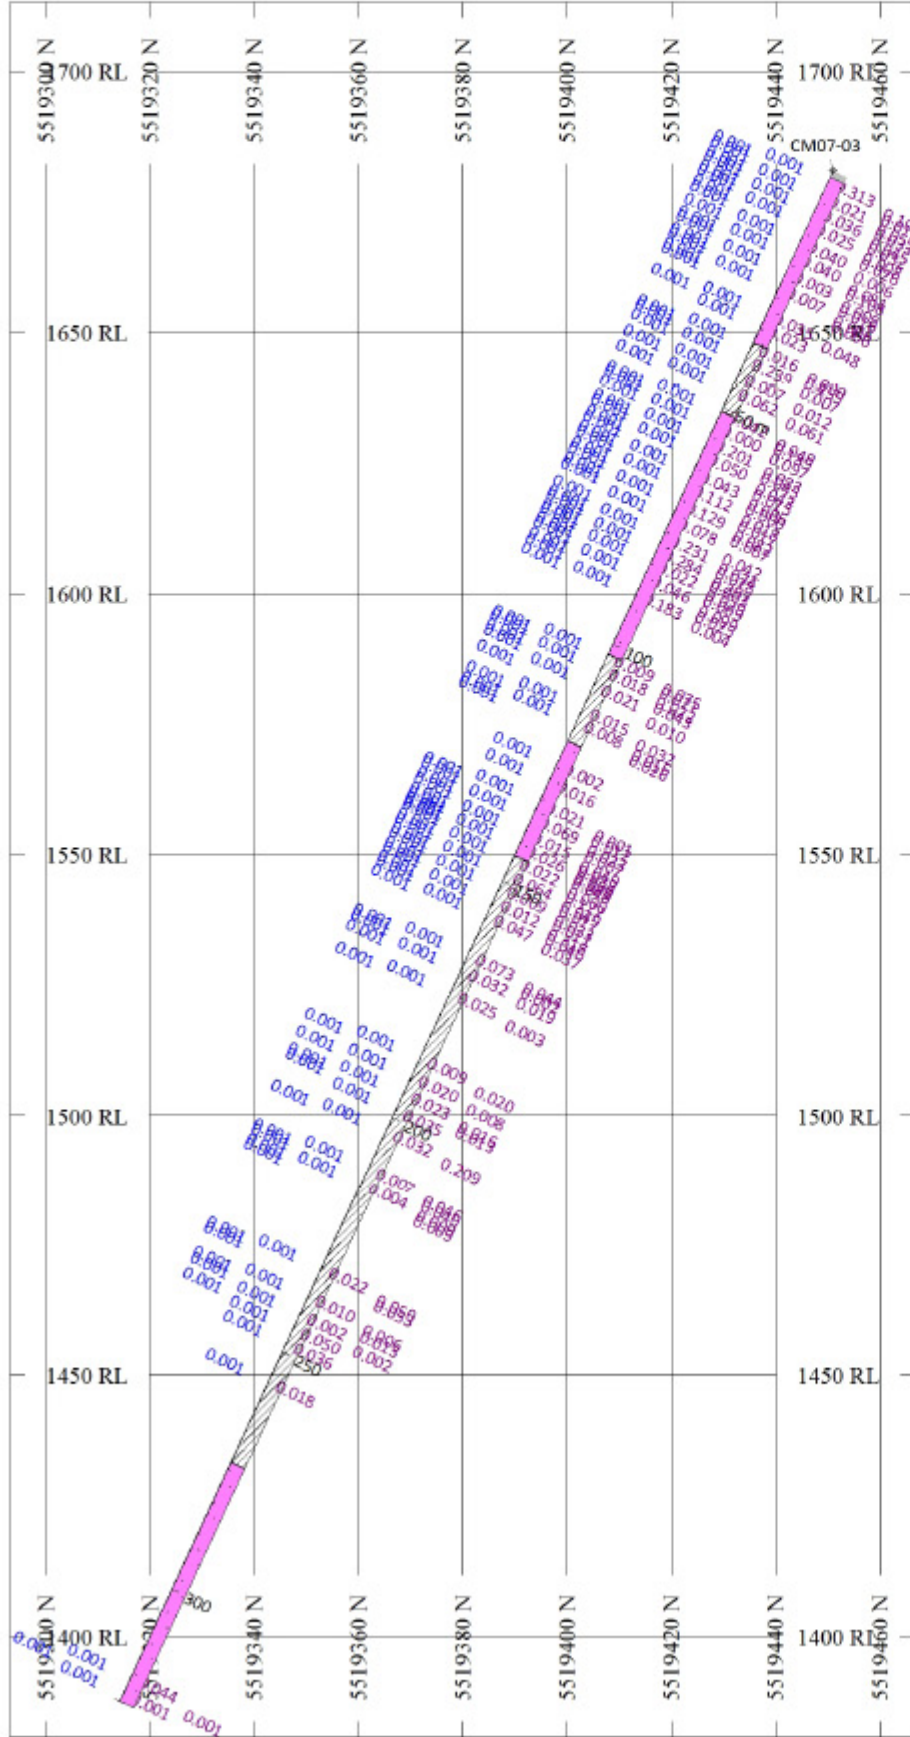

HOLES PLOTTED

TOTAL 1

CM07-03

ROCK CODES	L/R	PAT	LABEL	DESCRIPTION
Lithocode	R		BX	breccia
			NC	no core
			QP	quartz-porphry

ASSAYS	L/R	TEXT
Mo_pet	R	-----
W_pet	L	-----

SECTION SPECS:

REF. PT. E, N	585150 m	5519380 m
EXTENTS	173.9 m	332.5 m
SECTION TOP, BOT	1713 m	1381 m
TOLERANCE +/-	28.15 m	

SCALE 1 : 1500

(m)

*unknown

AZIMUTH = 0°

Pacific Cascade
Crack Moly
CM07-03

Mark Nelson, Nicolson & Assoc

Figure 8. Drill Section CM07-03

CM07-04 (Figure 9)

This was a short hole collared to test a zone of low chargeability. It encountered the same general lithologies as the others but no significant results were returned.

CM07-05 and 06 (Figure 10)

Both holes were collared from the same setup. Hole CM07-05 was testing a chargeability anomaly at depth; hole CM07-06 was a vertical hole testing lower chargeability and resistivity. Hole CM07-05 intersected a thick section of granodiorite to 131.45 metres, then intermixed quartz porphyry, breccia, and granodiorite to the bottom of the hole at 320.95 metres and returned the best assays of the program. The hole returned 0.053% molybdenite over 195.05 metres from 84.57 to 279.62 including 0.196% molybdenite over 44.60 metres. Hole CM07-06 intersected much more quartz porphyry and lesser granodiorite, monzonite and breccia units. The results were not as good as in CM07-05 with the interval from 1.52 to 110.00 metres averaging 0.029% molybdenum over 108.48 metres including 41.00 metres of 0.049% molybdenum.

CM07-07 (Figure 11)

Hole CM07-07 was collared approximately halfway between holes CM07-03 and CM07-05 to test the same chargeability feature at depth and intersected narrower intervals of monzonite and granodiorite near the top of the hole and then a broad zone of intermixed monzonite and heterolithic breccia with local sections of quartz porphyry. Traces of molybdenite were encountered throughout the hole but of insufficient density to form any broadly anomalous zones except at the top of the hole, which assayed 0.025% molybdenite over 44.18 metres from 1.82 to 46.00 metres.

CM07-08 (Figure 12)

The hole was collared in granodiorite and encountered no other lithologies, ending at 331.93 metres. The hole was collared in a high chargeability zone and attempted to test a high chargeability zone at depth, it did not fully reach the deep target as the depth capability of the drill was reached. Molybdenite was consistently present throughout the hole but in low concentrations, usually one or two narrow quartz-molybdenite veinlets per 1-3 metres. This low density veining was reflected in the assay results. Silver assays were elevated relative to



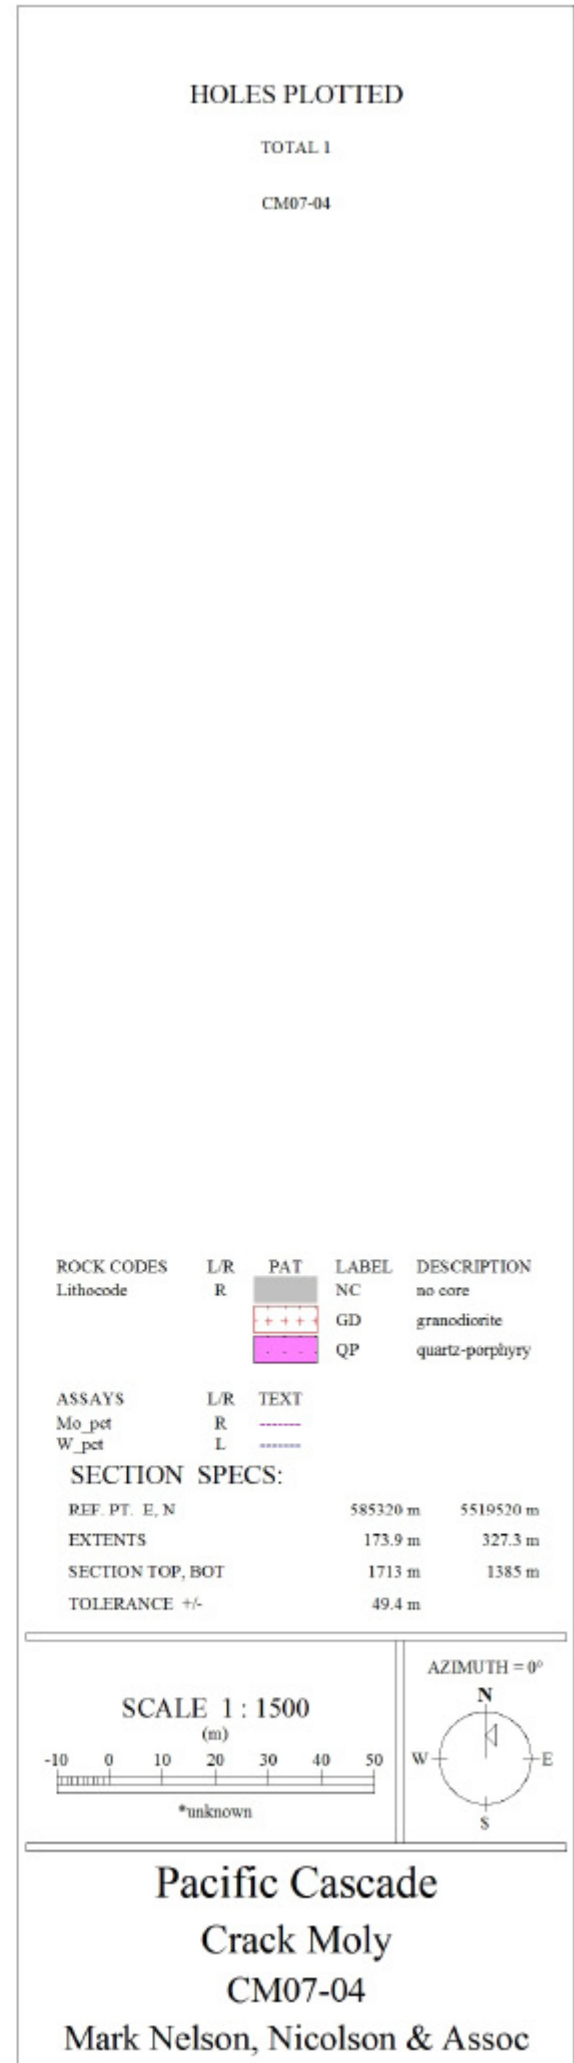


Figure 9. Drill Section CM07-04

585080 E						585080 E
						CM07-07
585100 E						585100 E

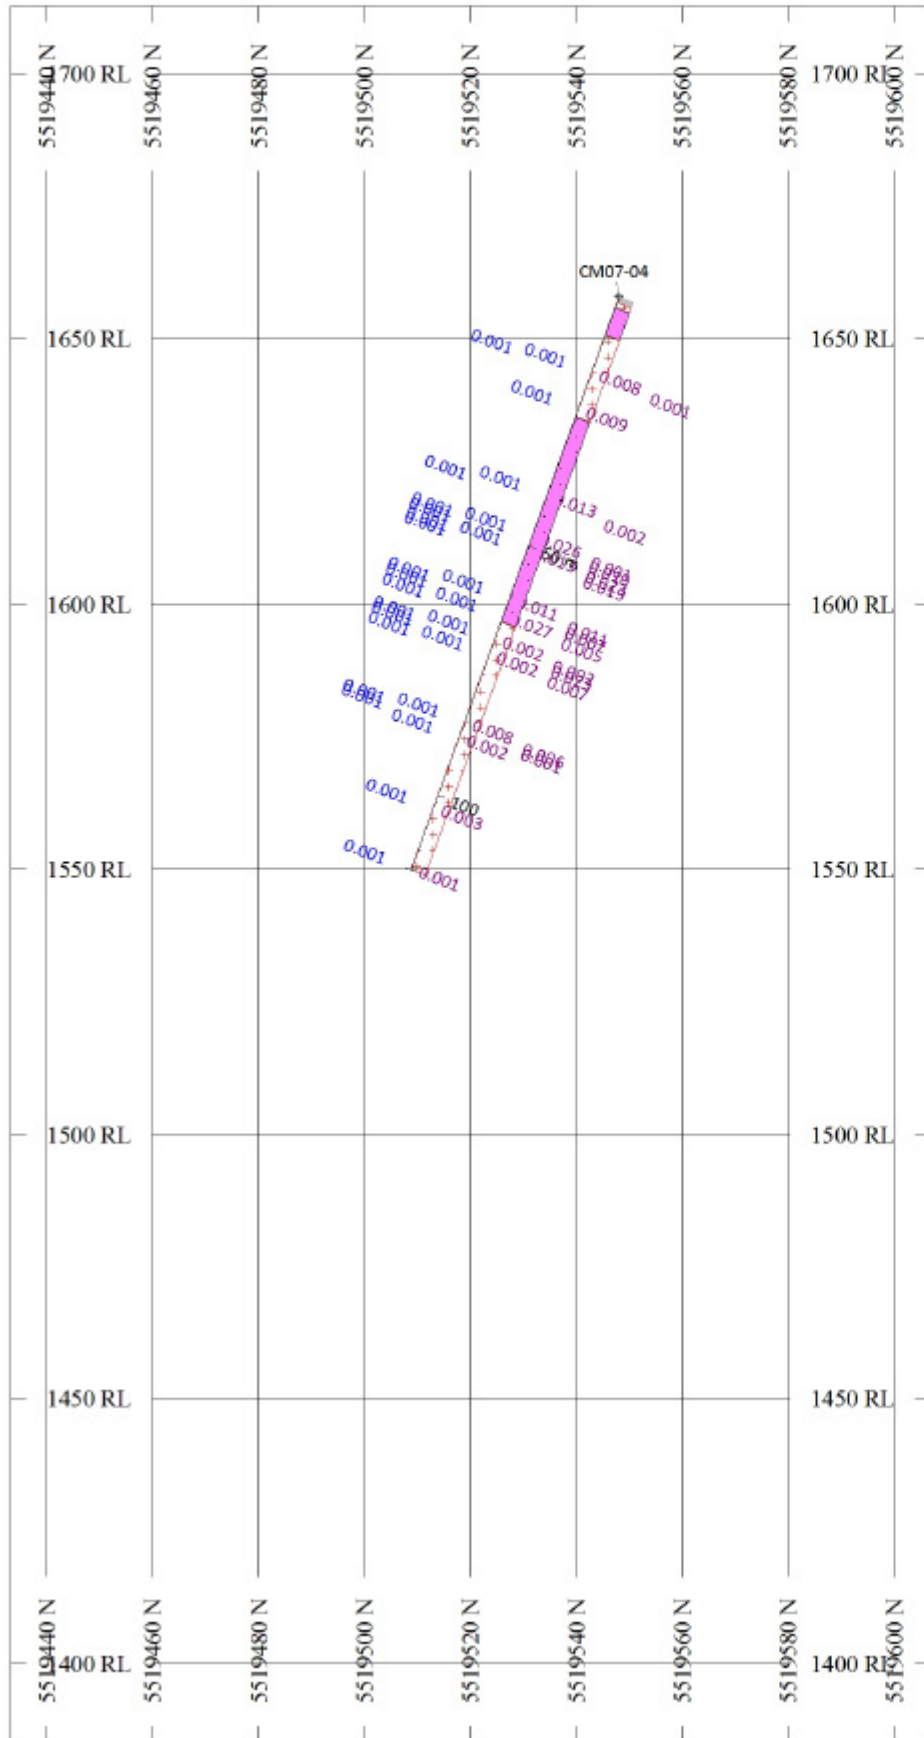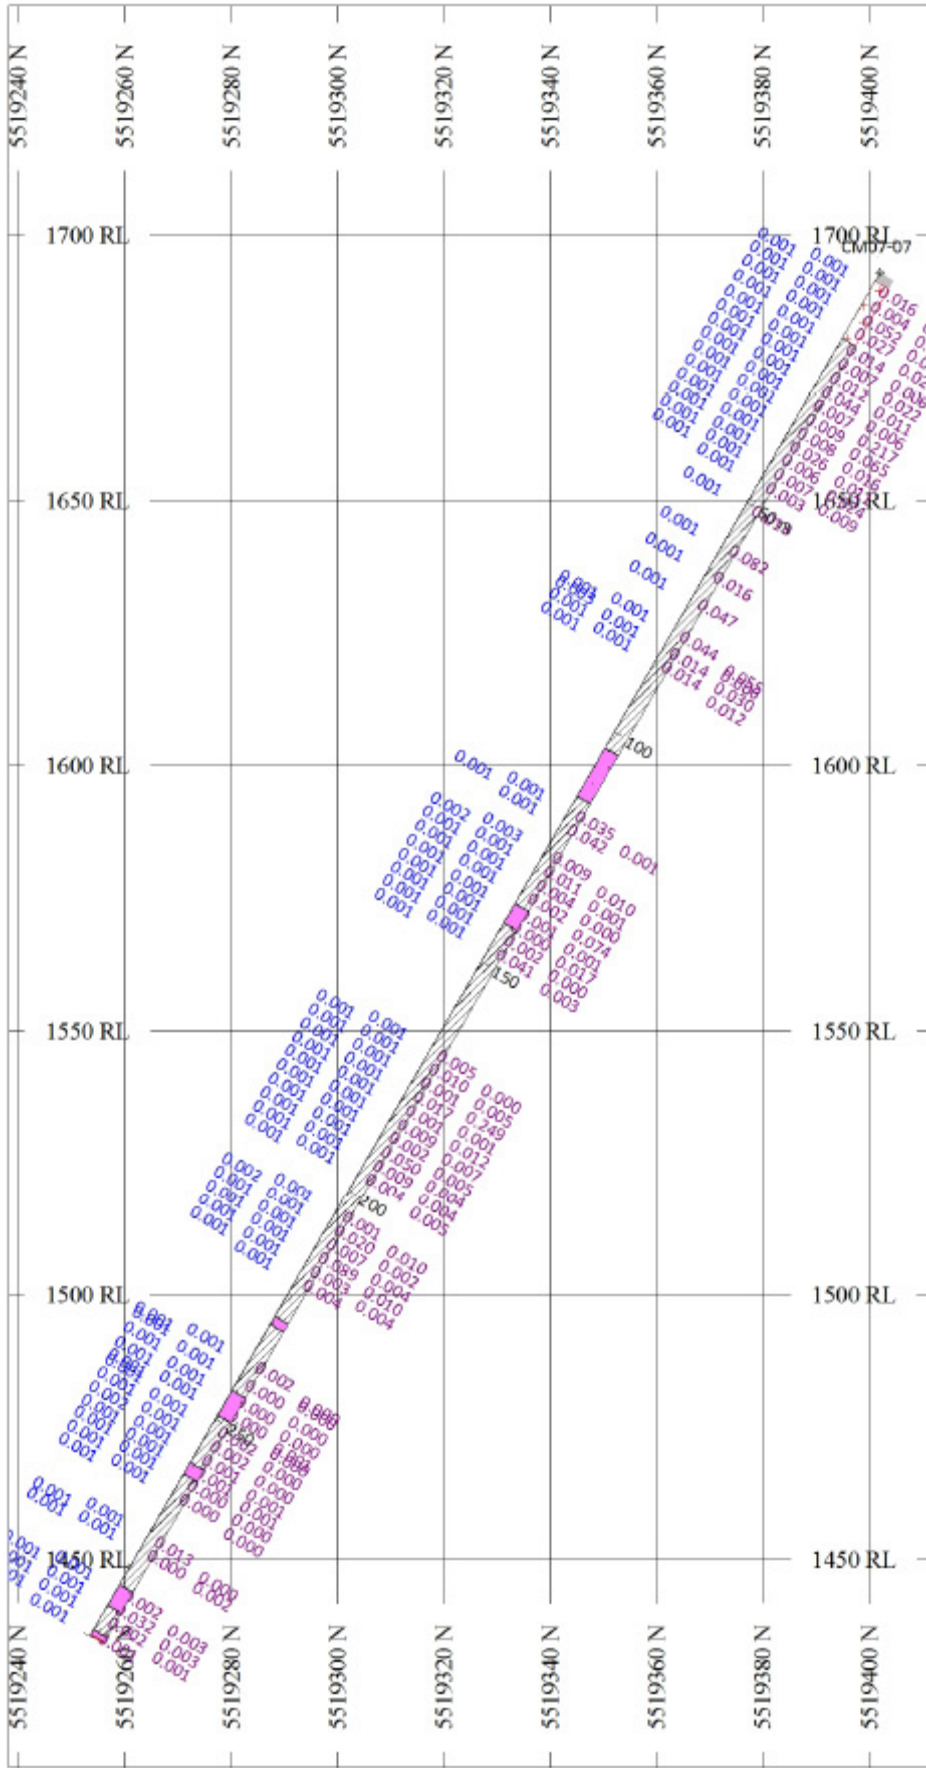

HOLES PLOTTED

TOTAL 1
CM07-07

ROCK CODES	L/R	PAT	LABEL	DESCRIPTION
Lithocode	R		BX	breccia
			NC	no core
			GD	granodiorite
			QP	quartz-porphyry

ASSAYS	L/R	TEXT
Mo_pct	R	-----
W_pct	L	-----

SECTION SPECS:

REF. PT. E, N	585096 m	5519325 m
EXTENTS	173.9 m	332.5 m
SECTION TOP, BOT	1743 m	1411 m
TOLERANCE +/-	31.39 m	

SCALE 1 : 1500
(m)

*unknown

AZIMUTH = 0°

**Pacific Cascade
Crack Moly
CM07-07
Mark Nelson, Nicolson & Assoc**

Figure 11. Drill Section CM07-07

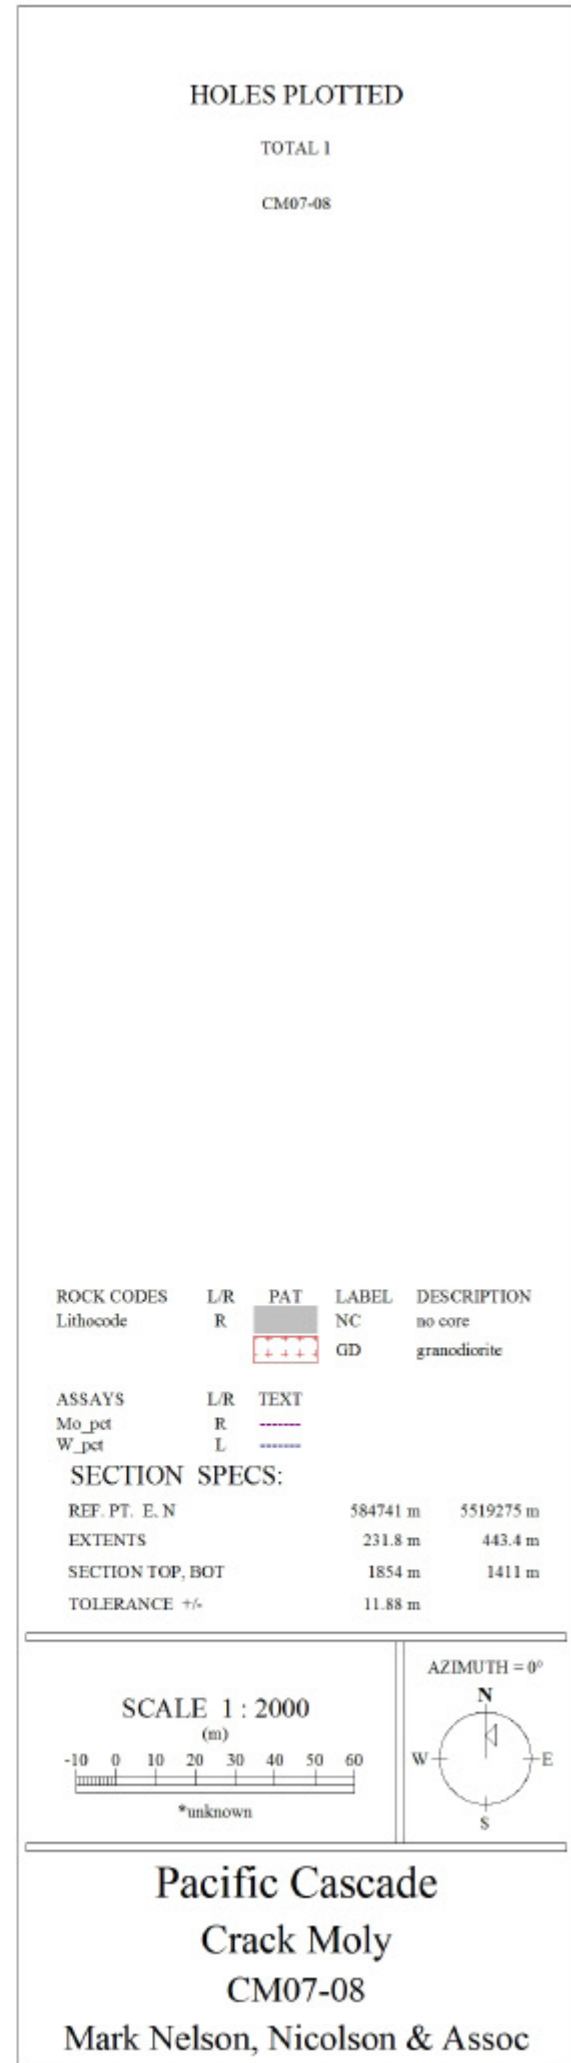
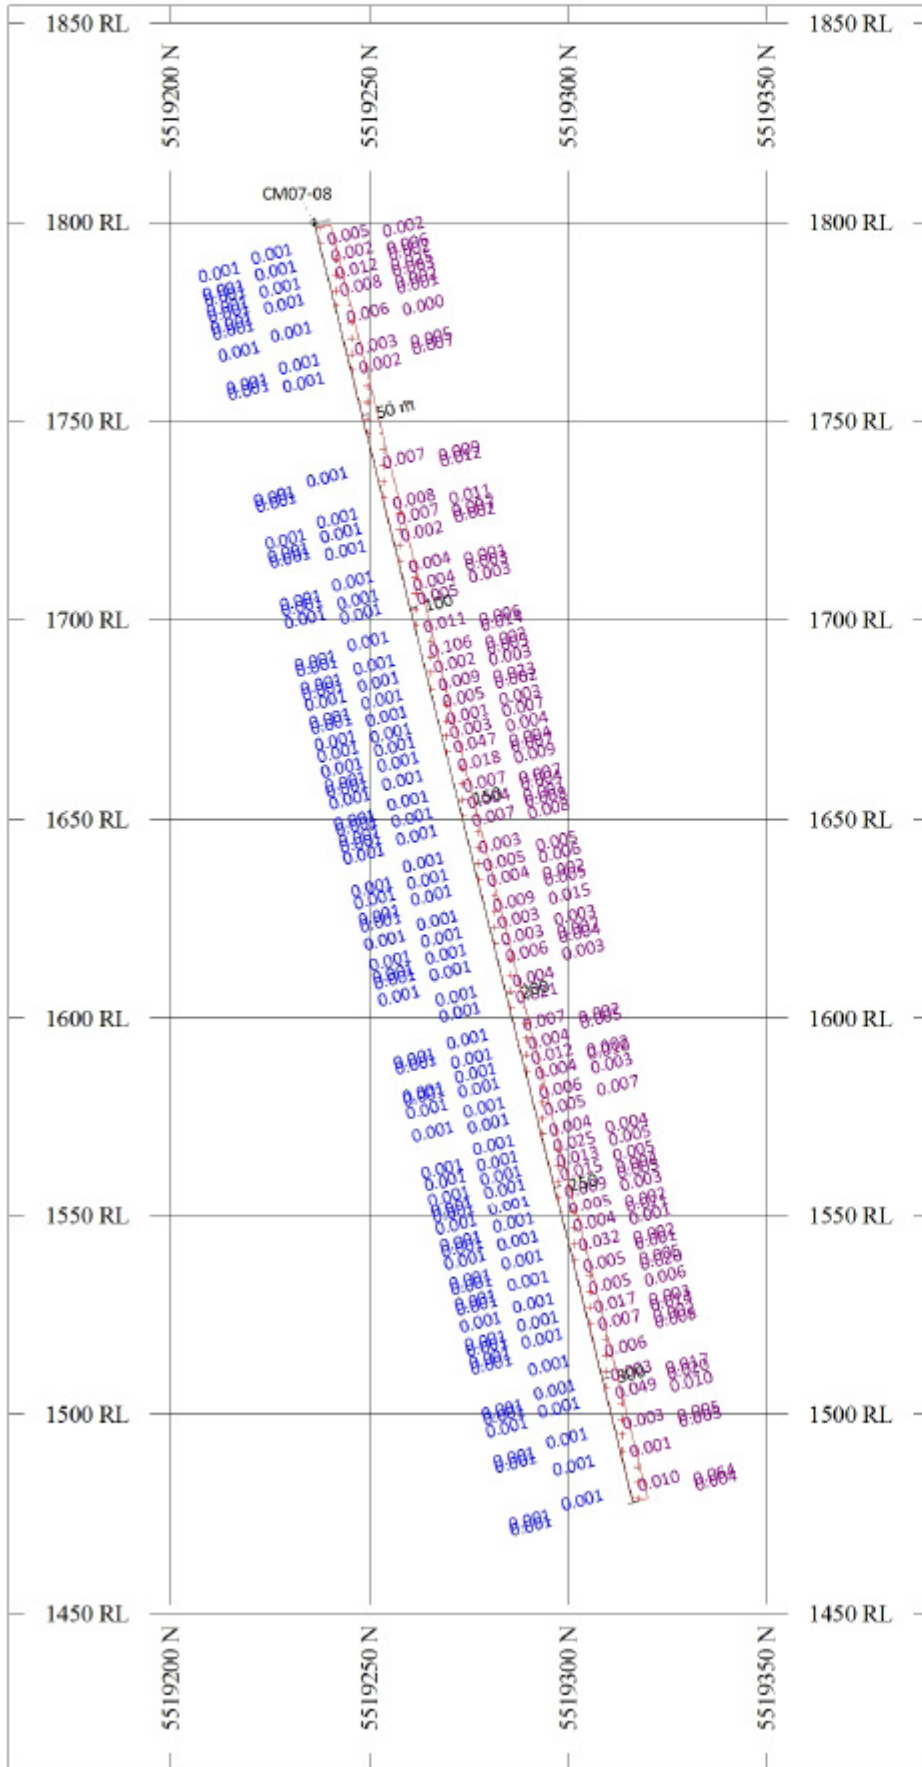


Figure 12. Drill Section CM07-08

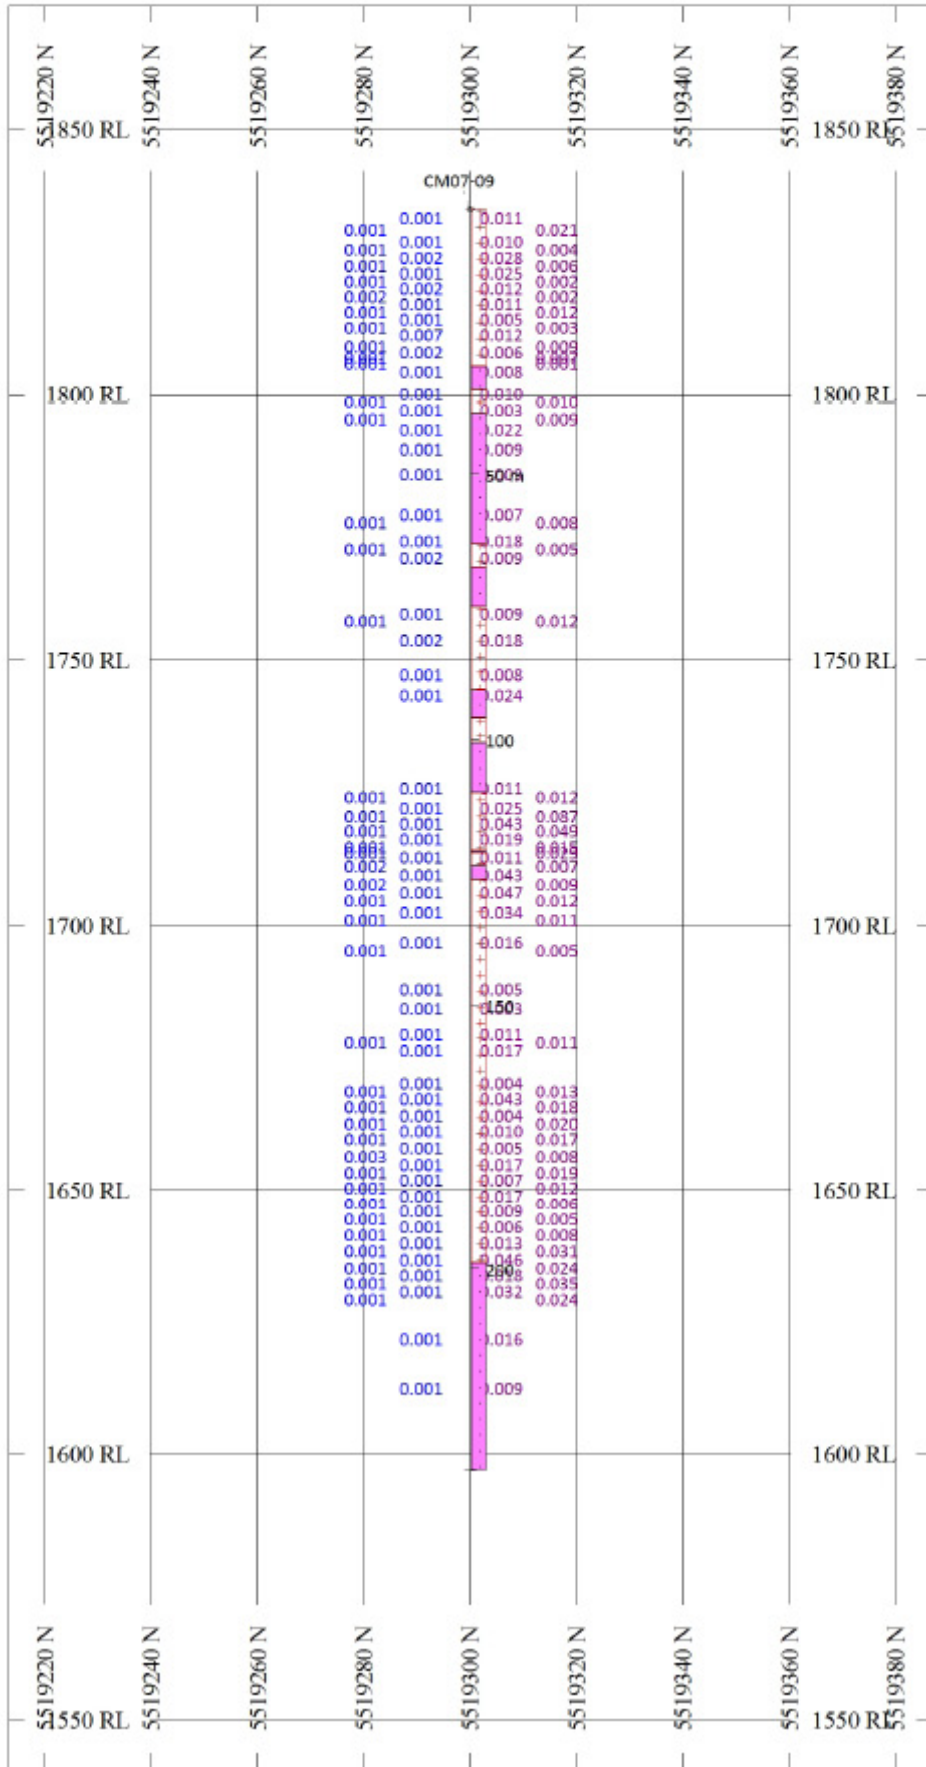
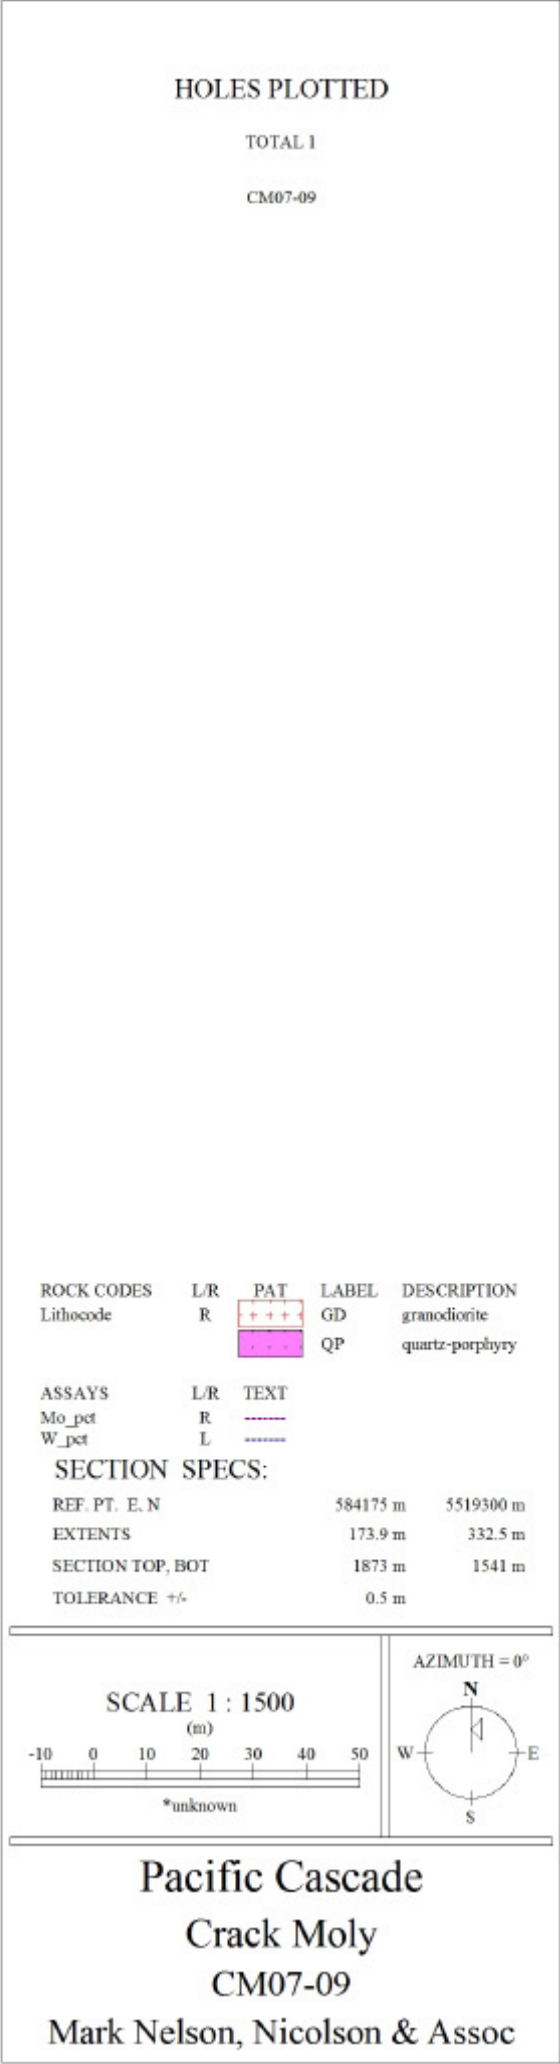
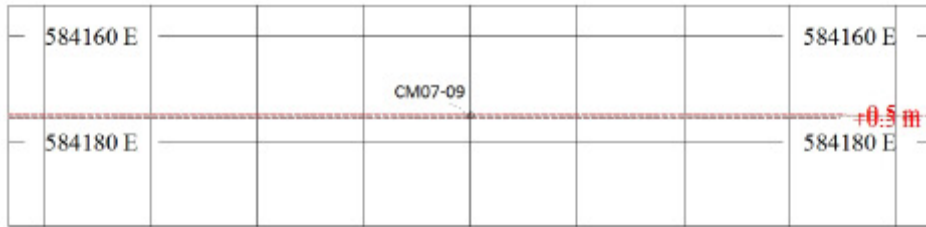


Figure 13. Drill Section CM07-09

any other hole with several intervals near the top of the hole reporting about 2.0 g/t silver over lengths of approximately seven metres.

CM07-09 (Figure 13)

The last hole of the program was also the westernmost hole drilled in 2007. It tested a strong surface chargeability feature but failed to fully test the deeper chargeability zone. The upper half of the hole intersected alternating granodiorite and quartz porphyry units followed by a thicker succession of granodiorite then quartz porphyry to the bottom of the hole. Assay results were low; the longest intercept was 42.63 metres averaging 0.017% molybdenite from 163.68 to 206.31 metres.

A summary of drill hole intercepts is presented in Table 3 - 2007 Drill Hole Intercepts

Table 3. 2007 Drill Hole Intercepts

Hole No.	From (metres)	To (metres)	Length (metres)	Mo (%)	Ag (ppm)	W (%)
CM07-01	121.95	124.55	2.60	0.109		
	187.41	343.51	156.1	0.035		
including	221.59	223.59	2.00			0.386
including	290.90	305.08	14.18	0.141		
including	301.81	304.80	2.99	0.437		
including	336.90	337.41	0.51	1.426		
CM07-02	29.78	30.84	1.06	0.114		
	129.15	130.15	1.00	0.219		
CM07-03	1.25	234.50	23.25	0.044		
	36.20	41.17	4.97	0.183		
including	37.20	40.15	2.95	0.300		
	64.77	90.53	25.76	0.080		
	132.73	159.60	26.87	0.136		
including	140.22	149.69	9.47	0.306		
including	142.65	143.16	0.51	3.320		
	202.13	204.10	1.97	0.117		

Hole No.	From (metres)	To (metres)	Length (metres)	Mo (%)	Ag (ppm)	W (%)
CM07-04	No significant results					
CM07-05	84.57	279.62	195.05	0.053%		
Including	140.8	185.40	44.60	0.196%		
Including	166.50	185.40	18.90	0.396%		
Including	177.62	185.40	7.78	0.936%		
Including	177.62	179.46	1.84	3.644%		
CM07-06	1.52	110.00	108.48	0.029		
including	59.50	100.50	41.00	0.049		
and including	70.00	73.00	3.00	0.128		
and including	85.50	100.50	15.00	0.062		
and including	85.50	91.50	6.00	0.088		
CM07-07	1.82	46.00	44.18	0.025		
including	28.00	32.50	4.50	0.097		
and including	28.00	29.50	1.50	0.217		
	175.50	177.00	1.50	0.249		
	212.50	214.00	1.50	0.089		
CM07-08	8.23	21.49	13.26	0.007	2.0	
	25.75	27.18	1.43	0.050		
	32.61	38.71	6.10	0.004	2.1	
	72.24	79.29	7.05	0.008	2.0	
	88.66	96.36	7.70	0.003	2.2	
	110.43	111.86	1.43	0.106		
	151.49	153.00	1.51	0.001	10.4	
	303.08	304.60	1.52	0.050		
	328.73	330.18	1.45	0.067		
	303.08	304.60	1.52	0.050		
	328.73	330.18	1.45	0.067		

Hole No.	From (metres)	To (metres)	Length (metres)	Mo (%)	Ag (ppm)	W (%)
CM07-09	111.86	130.90	19.04	0.030		
including	113.38	117.80	4.42	0.060		
	163.68	206.31	42.63	0.017		

7.4 DRILLING SUMMARY

The results of the program were encouraging. Several of the holes returned anomalous molybdenum assays over broad intervals of 100's of metres with local high-grade intercepts within. The drill was incapable of testing a very deep chargeability feature at an interpreted depth of 400-500 metres below surface so most of the drilling focused along the eastern margin of the deep-seated chargeability feature. The drilling tested and area nearly 700 metres in length with work focused along a ridge top due to the lack of helicopter support. There are targets to the north and west that remain untested as well as a deep-seated strong chargeability zone.

8. Conclusions and Recommendations

The drill program successfully tested various IP targets, including chargeability and resistivity highs, as well as areas of surface mineralization. An approximate length of 700 metres was drill tested with holes at variably spaced intervals along this trend, largely confined to sites along the ridge top. Casing was left in select holes so that they could be extended to depth to fully test the IP chargeability target.

Drilling has confirmed the presence of molybdenite mineralization over a widespread area. Locally higher grades over 10's of metres were received within broad (100's of metres) areas of lower grade material. Continuity of mineralization from hole to hole is not consistent, with lower grade zones separating higher-grade material. The best result of the program was from hole CM07-05, which assayed 0.053% molybdenite over 195.05 metres from 84.57 to 279.62 including 0.196% molybdenite over 44.60 metres.

The Company was not able to test a deep-seated IP chargeability anomaly interpreted at a depth of 400 to 500 metres below surface, as the onsite drill was too small. This target area occurs just west of the last hole completed, CM07-09 and remains a significant, untested target for 2008. The geophysical survey done in 2005 indicates possible extensions to the mineralization in the form of chargeability responses west of the last line surveyed, the survey should be expanded for coverage an additional 500 metres west and south to fully resolve both chargeability and resistivity targets.

9. Statement of Qualifications

9.1 WESLEY RAVEN

I, Wesley Raven, of 108-1720 West 12th Avenue, Vancouver, British Columbia hereby certify:

1. I am a graduate of the University of British Columbia (1983) and hold a BSc. degree in geology.
2. I have been employed in my profession with various companies since 1983.
3. I am a member of the Association of Professional Engineers and Geoscientists of British Columbia, and have been registered since 1992. I am also a Fellow of the Geological Association of Canada and have been a member since 1989.
4. I am responsible for preparation of all sections of this report utilizing data summarized in the References section of this report and from my time spent at onsite management and core logging on the property.
5. I have had no direct involvement with Pacific Cascade Minerals Inc. on the Crack Moly Property except for my time spent in preparing an 43-101 report and an assessment report.
6. I am not aware of any material fact or material change with respect to the subject matter of the report that is not reflected in the report, the omission to disclose which makes the assessment report misleading.
7. I am independent of Pacific Cascade Minerals Inc. and act as their "Qualified Person".
8. I consent to the use of this report by Pacific Cascade Minerals Inc. for any corporate use normal to their business.

Wesley Raven, P. Geo.

DATED at Vancouver, British Columbia, this 7th day of April, 2008

10. References

Christie, J.S., and Richards, G.G.,

1982: Geological and Geochemical Report, Scuzzy #1-2 Mineral Claims, December 21, 1982 (Assessment Report 11,003).

Geological Survey of Canada. Maps: 737A, 12-1969, 41-1989. Open Files: 482. Papers: 69-47.

Harivel, C.,

1981: Geochemical Report, Scuzzy #1 & #2 Mineral Claims, for Territorial Gold Placers Ltd. and JMT Services Corp., November 27, 1981 (Assessment Report 9793).

Nicholson, G., and Raven, W

2006: Geological, Geochemical, and Geophysical Report: Crack Moly Property (Scuzzy Showing), New Westminster Mining Division, for Pacific Cascade Minerals Inc., May 23, 2006.

Raven, W.,

2006: Geochemical and Geophysical Assessment Report on the Crack Moly Property (Scuzzy Showing), New Westminster Mining Division, for United Exploration Management Inc., April 2006.

Richards, G.G.,

1984: Geochemical Report, Scuzzy #1-2 Mineral Claims, December 21, 1984, (Assessment Report 13,384).

Sheldrake, R.,

2005: Data Processing and Interpretation Report, 3D Induced Polarization Geophysical Survey, Scuzzy Grid, Alt Grid, Crack Project, October 24, 2005.

12. Statement of Costs

Technical, Drilling (July 1, 2007 to December 15, 2007)

PERSONNEL	# days	rate/day	Totals
W. Raven at \$425.00/day	18.5	425	7,862.50
W. Raven at \$475.00/day	6.5	475	3,087.50
G. Nicholson at \$495.00/day	4	495	1,980.00
G. Barton at \$350/day	60	350	21,000.00
M. Hall at \$286/day	16	286	4,576.00
D. Williams at \$260/day	71	260	18,460.00
B. Langlois at \$260/day	8	260	2,080.00
S. Lowe at \$338/day	11	338	3,718.00
M. Mulberry at \$379.60/day	3	379.6	1,138.80
R. Belanger at \$390.00/day	38	390	14,820.00
N. Hewlett at \$260.00/day	22	260	5,720.00
J. Southall at \$260.00/day	22	260	5,720.00
G. Woloshyn at \$275.60/day	31	275.6	8,543.60
B. Vallee at \$312.00/day	7	312	2,184.00
J. Dick at 338/day	53.5	338	18,083.00
B. McMichael at \$244.40/day	68	244.4	16,619.20
B. Blondeau at \$182.00/day	15	182	2,730.00
GST for Rentals + Expenses + Contractors			12,343.82
EIC, CCP, WCB for payroll			8,520.98
Total Wages			159,187.40
EQUIPMENT RENTAL	# days	rate/day	
Truck Rental at \$95/day	44	\$90	3,960.00
Truck Rental at \$95/day	62	\$90	5,580.00
Truck Rental at \$95/day	16	\$90	1,440.00
Radios and Communication	3750	\$1	3,750.00
Camp Rental	8000	\$1	8,000.00
Total Equipment Rental			22,730.00
EXPENSES			
Motel/Hotel			3,379.11
Meals			1,476.84
Groceries			16,696.51
Camp Supplies			37,417.97
Fuels (trucks and snowmobiles)			4,753.65
Fuels (helicopter)			28,701.28
Fuels (camp and drill)			19,845.35
Field Equipment			4,818.73
Core Boxes and Core Saw Blades			6,956.05
Word Processing and Drafting			1,035.03
Miscellaneous			1,736.00
Communications			2,812.56
Travel (ferries, highway tolls, etc)			3,528.49
Vehicle repairs/supplies/parts			4,351.67
Office Overhead			16,000.00
Total Expenses			153,509.24
CONTRACTORS			
Eco Tech Laboratory Ltd.			21,907.31
1193 samples @ 18.36/sample including ICP and Mo assay			
ISE Blasting - drill pad construction & reclamation			42,257.56
Pacific Western helicopters - contract helicopter services			219,147.00
Westcore Drilling - 9 holes, BTW-core, 2437.49 metres			377,490.39
Total Contractors			660,802.26
TOTAL EXPENDITURES			\$996,228.90

Appendix 1.

Drill Logs

DIAMOND DRILL LOG

HOLE No. CM07-01

Property: Crack Moly	NTS:	Claim:	Elevation: 1749	Azimuth: n/a	Length: 343.51 m	Dip: -90°
Coordinates: 584864 E / 5519267 N	Dip Tests:		Advance:	Depth:	Date Collared: 09/08/07	Date Completed: 14/08/07
Purposes: IP Chargeability	Drilled by: Westcore Drilling		Assays by: Eco Tech		Logged by: M. Miller	

Interval		Rec'y %	Description	Sample No.	Interval		Core Width	Sample Description	Ag ppm	Cu ppm	Mo ppm	W ppm	Zn ppm
From	To				From	To							
0.00	1.26		Casing/Overburden										
1.26	10.08		Granodiorite; weathered hematite staining; small sections more siliceous; tr-<1% cpy, tr mo, py; calcite in veins parallel to core axis; weak foliation parallel to core axis; limit of oxidation = 10.08 m	6082001	1.26	3.40	2.14		0.4	59	18	<10	99
				6082002	3.40	5.18	1.78		0.4	116	62	<10	69
				6082003	5.18	6.80	1.62		0.6	169	34	<10	64
				6082004	6.80	8.23	1.43		0.4	16	22	<10	85
				6082005	8.23	9.23	1.00		0.4	153	23	<10	122
				6082006	9.23	10.23	1.00		0.2	1728	160	<10	88
10.08	15.00		Granodiorite; below weathering; has qtz veins at 20° to CA with mo; silica alteration zones	6082007	10.23	11.28	1.05	STANDARD	<0.2	55	56	<10	70
				6082008	11.28	12.38	1.10		<0.2	18	24	<10	65
				6082009	12.38	14.38	2.00		<0.2	23	22	<10	104
				6082010									
15.00	31.66		Foliated Granodiorite; weak fabric/foliation; micro fractures carry tr cpy; small qtz filled x-cutting veinlets (<1 cm) at 30° to CA carry very fine-grained mo + possible py, vein density is 1/2.5 metres	6082011	14.38	15.38	1.00		0.2	62	63	<10	62
				6082012	15.38	16.38	1.00		0.2	55	54	<10	71
				6082013	16.38	17.38	1.00		0.2	33	100	<10	70
				6082014	17.38	18.38	1.00		<0.2	2	524	<10	46
				6082015	18.38	19.39	1.01		<0.2	17	362	<10	57
				6082016	19.39	20.42	1.03		<0.2	13	104	<10	54
				6082017	20.42	21.97	1.55		<0.2	76	35	<10	165

DIAMOND DRILL LOG

HOLE No. CM07-01

Interval		Rec'y %	Description	Sample No.	Interval		Core Width	Sample Description	Ag ppm	Cu ppm	Mo ppm	W ppm	Zn ppm
From	To				From	To							
				6082018	21.97	23.47	1.50		<0.2	36	89	<10	77
				6082019	23.47	25.47	2.00		0.4	120	207	<10	68
				6082020	25.47	26.50	1.03		0.2	133	210	<10	82
				6082021	26.50	27.50	1.00		1.2	632	381	<10	107
				6082022	27.50	29.50	2.00		0.2	16	185	<10	58
				6082023				STANDARD					
				6082024	29.50	31.50	2.00		<0.2	42	254	<10	51
				6082025	31.50	33.60	2.10		<0.2	55	55	<10	93
31.66	44.56		Quartz Porphyry; fine-grained, fractured and broken; red alteration with envelopes of mafic (aphanitic) mineral around fine-grained fractures healed with quartz, py, mo; aphanitic texture with 3% grey flecks, partings have fn-gr mo; short sections contain po	6082026	33.60	35.60	2.00		0.4	96	98	<10	88
				6082027	35.60	36.44	0.84		1	289	63	<10	528
				6082028	36.44	37.50	1.06		2.8	1580	66	<10	339
				6082029	37.50	38.50	1.00		1	287	81	<10	154
				6082030	38.50	39.55	1.05		0.6	522	103	<10	173
				6082031	39.55	40.60	1.05		1	548	108	<10	148
				6082032	40.60	41.76	1.16		0.6	220	66	<10	379
				6082033				BLANK					
				6082034	41.76	42.80	1.04		0.4	107	29	<10	746
				6082035	42.80	43.80	1.00		0.4	109	38	<10	83
				6082036	43.80	44.56	0.76		0.4	102	58	<10	150

DIAMOND DRILL LOG

HOLE No. CM07-01

Interval		Rec'y %	Description	Sample No.	Interval		Core Width	Sample Description	Ag ppm	Cu ppm	Mo ppm	W ppm	Zn ppm
From	To				From	To							
				6082058	70.07	72.15	2.08		0.6	111	114	<10	284
				6082059	72.15	74.18	2.03		0.4	84	170	<10	104
				6082060	74.18	76.20	2.02		0.4	10	52	<10	59
				6082061	76.20	78.22	2.02		0.2	10	29	<10	71
				6082062	78.22	80.02	1.80		0.6	44	81	<10	112
				6082063	80.02	81.08	1.06		0.4	70	107	<10	77
				6082064	81.08	82.10	1.02		0.4	99	99	<10	93
				6082065	82.10	84.20	2.10		0.2	46	51	<10	117
				6082066	84.20	86.25	2.05		<0.2	37	113	<10	143
				6082067	86.25	87.37	1.12		<0.2	89	75	<10	85
				6082068	87.37	88.42	1.05		0.2	21	42	<10	68
				6082069				STANDARD					
				6082070	88.42	89.46	1.04		<0.2	41	48	<10	80
				6082071	89.46	90.52	1.06		0.4	23	63	<10	108
				6082072	90.52	91.53	1.01		0.2	85	188	<10	165
				6082073	91.53	92.55	1.02		0.2	218	741	<10	438
				6082074	92.55	93.50	0.95		0.2	103	46	<10	414
93.50	148.38		Quartz Porphyry; fractured and annealed; altered to unaltered; occasional granitic lithic fragments; aphanitic, quartzite matrix; mo + fe minerals very fn-gr; also minor py + cpy, broken zones: 96.00-98.60 m, 100.60-101.00 m, 102.70-103.20 m, 108.55-109.25 m	6082075	93.50	94.55	1.05		0.2	36	157	<10	59
				6082076	94.55	96.62	2.07		0.2	54	49	<10	83
				6082077	96.62	97.67	1.05		0.4	32	48	<10	29
				6082078	97.67	98.79	1.12		0.2	55	89	<10	115

DIAMOND DRILL LOG

HOLE No. CM07-01

Interval		Rec'y %	Description	Sample No.	Interval		Core Width	Sample Description	Ag ppm	Cu ppm	Mo ppm	W ppm	Zn ppm
From	To				From	To							
				6082079				STANDARD					
				6082080	98.79	99.97	1.18		0.2	43	93	<10	109
				6082081	99.97	100.90	0.93		0.4	32	41	<10	165
				6082082	100.90	102.05	1.15		0.2	25	76	<10	76
				6082083	102.05	103.21	1.16		0.4	48	23	<10	145
				6082084	103.21	104.80	1.59		0.4	105	45	<10	66
				6082085	104.80	105.79	0.99		0.2	31	73	<10	43
				6082086	105.79	106.79	1.00		0.2	65	53	<10	114
				6082087	106.79	107.81	1.02		0.4	48	127	<10	41
				6082088	107.81	108.81	1.00		0.2	28	80	<10	33
				6082089	108.81	109.55	0.74		0.4	46	38	<10	35
				6082090	109.55	110.89	1.34		0.4	57	76	<10	87
				6082091	110.89	111.86	0.97		0.4	19	45	<10	25
				6082092	111.86	112.87	1.01		0.4	24	143	<10	38
				6082093	112.87	113.89	1.02		0.4	33	24	<10	51
				6082094	113.89	114.91	1.02		0.4	53	65	<10	33
				6082095				STANDARD					
				6082096	114.91	115.91	1.00		0.2	30	21	<10	34
				6082097	115.91	116.91	1.00		0.4	56	57	<10	89
				6082098	116.91	117.96	1.05		0.2	23	16	<10	19
				6082099	117.96	118.98	1.02		0.4	20	30	<10	31

DIAMOND DRILL LOG

HOLE No. CM07-01

Interval		Rec'y %	Description	Sample No.	Interval		Core Width	Sample Description	Ag ppm	Cu ppm	Mo ppm	W ppm	Zn ppm
From	To				From	To							
				6082100	118.98	120.00	1.02		0.4	30	15	<10	42
				6082101	120.00	121.01	1.01		0.6	45	17	<10	39
				6082102	121.01	121.95	0.94		0.6	31	24	<10	39
				6082103	121.95	123.05	1.10		1.2	57	1627	<10	32
				6082104	123.05	124.05	1.00		0.4	85	108	<10	47
				6082105	124.05	124.55	0.50		0.6	96	1860	<10	140
				6082106	124.55	125.50	0.95		0.2	28	106	<10	72
				6082107	125.50	126.40	0.90		0.4	35	37	<10	49
				6082108	126.40	127.40	1.00		0.2	31	27	<10	46
				6082109				STANDARD					
				6082110				BLANK					
				6082111	127.40	128.42	1.02		0.4	46	26	<10	116
				6082112	128.42	130.45	2.03		0.2	20	176	<10	54
				6082113	130.45	131.45	1.00		0.8	27	53	<10	159
				6082114	131.45	132.50	1.05		5.2	213	88	<10	275
				6082115	132.50	133.44	0.94		0.2	25	45	<10	61
				6082116	133.44	135.44	2.00		0.2	35	40	<10	40
				6082117	135.44	137.44	2.00		0.2	26	32	<10	35
				6082118				BLANK					
				6082119	137.44	139.59	2.15		<0.2	27	43	<10	36
				6082120	139.59	140.59	1.00		0.2	52	33	<10	45

DIAMOND DRILL LOG

HOLE No. CM07-01

Interval		Rec'y %	Description	Sample No.	Interval		Core Width	Sample Description	Ag ppm	Cu ppm	Mo ppm	W ppm	Zn ppm	
From	To				From	To								
				6082121	140.59	142.34	1.75		0.2	39	75	<10	113	
				6082122	142.34	143.34	1.00		0.2	39	85	<10	43	
				6082123	143.34	144.40	1.06		0.2	23	28	<10	48	
				6082124	144.40	145.39	0.99		0.2	29	97	<10	84	
				6082125	145.39	146.54	1.15		0.2	45	198	<10	115	
				6082126	146.54	147.48	0.94		0.4	17	441	<10	101	
				6082127	147.48	148.38	0.90		0.2	18	38	<10	227	
148.38	150.77		Granodiorite; hornblende + biotite; mo seams < 1 cm wide	6082128	148.38	150.77	2.39		0.3	40	408	10	94	
150.77	155.04		Quartz Porphyry; as previously described	6082129	150.77	152.18	1.41	STANDARD	0.2	22	112	<10	39	
				6082130										
				6082131	152.18	153.62	1.44		0.2	27	61	40	50	
				6082132	153.62	155.04	1.42		0.3	24	17	<10	28	
155.04	159.98		Granodiorite; as 148.38-150.77 m	6082133	155.04	157.10	2.06		<0.2	34	283	30	58	
				6082134	157.10	159.00	1.90		0.2	59	203	<10	62	
				6082135	159.00	159.98	0.98		<0.2	7	147	<10	65	
159.98	173.77		Altered Hornblende-Biotite/Quartz Porphyry	6082136	159.98	161.15	1.17	STANDARD	<0.2	24	195	<10	53	
				6082137	161.15	162.55	1.40		0.2	41	275	<10	58	
				6082138	162.55	163.77	1.22		0.2	22	93	40	89	
				6082139										
				6082140	163.77	165.04	1.27		0.3	39	27	<10	72	
				6082141	165.04	166.58	1.54		0.4	9	161	<10	34	

DIAMOND DRILL LOG

HOLE No. CM07-01

Interval		Rec'y %	Description	Sample No.	Interval		Core Width	Sample Description	Ag ppm	Cu ppm	Mo ppm	W ppm	Zn ppm
From	To				From	To							
				6082142	166.58	168.25	1.67		0.4	19	17	<10	37
				6082143	168.25	170.25	2.00		0.2	73	120	<10	123
				6082144	170.25	172.30	2.05		0.2	36	140	<10	76
				6082145	172.30	174.72	2.42		0.2	30	0.058%	<10	64
173.77	181.12		Quartz Porphyry	6082146	174.72	175.61	0.89		<0.2	16	28	<10	40
				6082147	175.61	177.56	1.95		0.3	19	48	<10	28
				6082148	177.56	179.69	2.10		0.2	51	95	<10	54
				6082149	179.69	181.12	1.46		0.4	10	14	<10	28
181.12	185.69		Hornblende-Biotite / Granodiorite; fractured	6082150	181.12	183.14	2.02		<0.2	44	0.061%	<10	63
				6082151	183.14	185.65	2.51		0.4	74	77	<10	103
185.69	188.87		Grandodiorite	6082152	187.14	188.87	1.73		0.2	12	25	<10	55
188.87	205.58		Hornblende-Biotite / Granodiorite; fractured / Quartz Porphyry	6082153	188.87	190.95	2.08		0.4	33	75	<10	67
				6082154				STANDARD					
				6082155	190.95	192.95	2.00		0.2	45	184	<10	136
				6082156	192.95	194.05	1.55		<0.2	41	235	<10	65
				6082157	194.05	195.66	1.16		0.6	46	292	<10	96
				6082158	195.66	196.76	1.10		0.2	28	18	<10	31
				6082159	196.76	197.80	1.04		0.4	49	306	<10	47
				6082160	197.80	198.80	1.00		0.3	28	97	<10	18
				6082161	198.80	199.94	0.14		0.6	49	94	<10	37
				6082162	199.94	200.25	1.31		0.4	29	38	<10	53

DIAMOND DRILL LOG

HOLE No. CM07-01

Interval		Rec'y %	Description	Sample No.	Interval		Core Width	Sample Description	Ag ppm	Cu ppm	Mo ppm	W ppm	Zn ppm
From	To				From	To							
				6082163	200.25	201.25	1.00		0.6	6	189	<10	43
				6082164	201.25	202.21	0.96		0.5	12	87	<10	54
				6082165	202.21	203.30	1.09		0.3	10	0.086%	<10	67
				6082166	203.30	204.28	1.18		0.2	25	201	<10	62
				6082167	204.28	205.28	1.00		0.3	39	80	<10	37
205.58	244.10		Hornblende – Biotite; large section of melange, variable qtz content as veinlets + small veins; mo partings common; small QP sections may be larger fragments	6082168	205.28	206.30	1.02		0.2	42	231	<10	51
				6082169	206.30	207.32	1.02		0.5	110	143	<10	65
				6082170	207.32	208.34	1.02		0.8	37	70	<10	66
				6082171				STANDARD					
				6082172	208.34	209.39	1.05		0.4	116	0.050%	<10	73
				6082173	209.39	210.40	1.01		0.6	80	38	<10	62
				6082174	210.40	211.40	1.00		<0.2	25	288	<10	42
				6082175	211.40	212.45	1.05		0.6	41	72	<10	82
				6082176	212.45	214.00	1.55		0.5	34	107	<10	57
				6082177	214.00	215.00	1.00		<0.2	61	316	<10	47
				6082178	215.00	215.58	0.58		0.5	23	53	<10	21
				6082179	215.58	217.60	2.02		0.4	23	36	<10	47
				6082180	217.60	219.60	2.00		0.4	39	137	20	44
				6082181	219.60	221.59	1.99		0.6	31	0.054%	20	71
				6082182				BLANK					
				6082183	221.59	222.59	1.00		0.6	66	0.024%	0.084%	55

DIAMOND DRILL LOG

HOLE No. CM07-01

Interval		Rec'y %	Description	Sample No.	Interval		Core Width	Sample Description	Ag ppm	Cu ppm	Mo ppm	W ppm	Zn ppm
From	To				From	To							
				6082184	222.59	223.59	1.00		0.4	76	165	0.688%	138
				6082185	223.59	225.59	2.00		0.6	45	171	<10	114
				6082186	225.59	227.47	1.88		0.6	72	144	<10	69
				6082187				STANDARD					
				6082188	227.47	229.49	2.02		0.4	39	153	10	51
				6082189	229.49	231.40	1.91		0.4	36	36	<10	44
				6082190	231.40	233.38	1.98		0.6	32	419	<10	49
				6082191	233.38	235.50	2.12		0.6	126	182	0.126%	53
				6082192	235.50	237.60	2.10		0.4	19	149	<10	52
				6082193				STANDARD					
				6082194	237.60	238.60	1.00		0.2	51	240	<10	46
				6082195	238.60	239.60	1.00		0.4	29	64	<10	53
				6082196	239.60	240.60	1.00		0.4	26	47	<10	43
				6082197	240.60	242.10	1.50		5.0	21	57	<10	47
			242.00-244.10 m: bio rich matrix	6082198	242.10	244.10	2.00		0.5	53	389	<10	50
244.10	249.02		Hornblende Biotite / Quartz Porphyry	6082199	244.10	246.15	2.05		0.6	24	150	110	39
				6082200	246.15	248.15	2.00		0.3	22	92	<10	51
				6082201	248.15	249.20	1.05		0.4	17	169	<10	53
249.02	250.92		Quartz Porphyry	6082202	249.20	250.92	1.72		0.4	26	42	<10	21
250.92	306.50		Hornblende Biotite; as described 205.58-244.10 m	6082203	250.92	252.90	1.98		0.5	31	37	<10	51
				6082204	252.90	254.90	2.00		0.4	36	0.063%	<10	51

DIAMOND DRILL LOG

HOLE No. CM07-01

Interval		Rec'y %	Description	Sample No.	Interval		Core Width	Sample Description	Ag ppm	Cu ppm	Mo ppm	W ppm	Zn ppm
From	To				From	To							
				6082205	254.90	256.05	1.15		0.3	33	477	120	45
				6082206				STANDARD					
				6082207	256.05	257.05	1.00		0.4	76	0.074%	60	54
				6082208	257.05	259.02	1.97		0.4	29	53	<10	47
				6082209	259.02	260.30	1.28		0.5	39	30	<10	21
				6082210	260.30	262.35	2.05		0.5	80	83	<10	41
				6082211	262.35	264.35	2.00		0.7	69	270	<10	43
				6082212	264.35	266.40	2.05		0.3	45	242	<10	46
				6082213	266.40	268.40	2.00		0.6	64	43	<10	49
				6082214				STANDARD					
				6082215	268.40	270.36	1.96		0.5	83	178	<10	49
				6082216	270.36	272.36	2.00		0.3	53	156	<10	48
				6082217	272.36	274.36	2.00		0.5	101	225	<10	47
				6082218	274.36	276.30	1.94		0.4	33	197	50	45
				6082219	276.30	278.30	2.00		0.2	50	187	<10	47
				6082220	278.30	280.30	2.00		<0.2	60	96	<10	57
				6082221	280.30	281.30	1.00		<0.2	56	276	<10	63
				6082222	281.30	283.25	1.95		0.4	71	401	<10	58
				6082223	283.25	284.20	0.95		1.4	790	141	<10	75
				6082224	284.20	285.13	0.93		0.2	42	361	<10	63
				6082225	285.13	287.15	2.02		0.4	53	302	<10	41

DIAMOND DRILL LOG

HOLE No. CM07-01

Interval		Rec'y %	Description	Sample No.	Interval		Core Width	Sample Description	Ag ppm	Cu ppm	Mo ppm	W ppm	Zn ppm
From	To				From	To							
				6082226				STANDARD					
				6082227				BLANK					
				6082228	287.15	288.90	1.75		0.2	31	0.072%	<10	49
				6082229	288.90	290.90	2.00		0.3	35	80	<10	32
				6082230	290.90	292.90	2.00		<0.2	108	390	<10	42
				6082231	292.90	294.80	1.90		<0.2	78	369	<10	42
				6082232	294.80	295.80	1.00		0.2	53	373	<10	41
				6082233	295.80	296.80	1.00		<0.2	70	0.066%	<10	47
				6082234	296.80	297.77	0.97		0.2	117	0.328%	<10	32
				6082235	297.77	298.80	1.03		0.5	33	107	<10	14
				6082236				STANDARD					
				6082237	298.80	300.84	2.04		<0.2	76	368	<10	43
				6082238	300.84	301.81	0.97		0.2	77	112	<10	38
				6082239	301.81	302.85	1.04		0.2	172	0.323%	<10	44
				6082240	302.85	303.80	0.95		<0.2	49	0.655%	<10	31
				6082241	303.80	304.80	1.00		0.3	55	0.363%	<10	33
				6082242	304.80	305.80	1.00		<0.2	99	284	<10	37
				6082243	305.80	306.80	1.00		<0.2	169	205	<10	36
306.50	309.83		Quartz Porphyry / Hornblende Biotite; mixed unit, mo partings and rosettes in qtz vein	6082244	306.80	307.80	1.00		<0.2	88	180	<10	40
				6082245	307.80	308.80	1.00		0.4	74	89	<10	29
				6082246	308.80	309.83	1.03		2.6	955	12	<10	80

DIAMOND DRILL LOG

HOLE No. CM07-01

Interval		Rec'y %	Description	Sample No.	Interval		Core Width	Sample Description	Ag ppm	Cu ppm	Mo ppm	W ppm	Zn ppm	
From	To				From	To								
				6082247				STANDARD						
309.83	332.55		Granodiorite; mixed massive to foliated; small partings and veinlets	6082248	309.83	310.80	0.97		0.5	292	68	<10	46	
				6082249	310.80	312.79	1.99		1.2	399	27	<10	66	
				6082250	312.79	314.80	2.01		0.2	42	220	<10	37	
				6082251	314.80	316.74	1.94		<0.2	27	30	<10	38	
				6082252	316.74	318.84	2.10		<0.2	22	10	<10	48	
				6082253	318.84	320.85	2.01		<0.2	73	92	<10	47	
				6082254	320.85	322.87	2.02		0.4	107	0.072%	<10	44	
				6082255					STANDARD					
				6082256	322.87	324.68	1.81		0.4	44	52	<10	46	
				6082257					STANDARD					
				6082258	324.68	326.64	1.96		0.3	46	141	<10	44	
				6082259	326.64	328.70	2.06		<0.2	58	172	<10	42	
				6082260	328.70	329.55	0.85		<0.2	127	301	20	43	
				6082261	329.55	330.52	0.97		<0.2	88	0.080%	<10	43	
			6082262	330.52	332.55	2.03		0.4	90	221	<10	47		
332.55	338.45		Granodiorite; broken rock with mo partings and interstitial blebs	6082263	332.55	334.50	1.95		0.3	34	16	<10	57	
				6082264	334.50	336.39	1.89		0.6	88	67	<10	53	
				6082265					STANDARD					
				6082266	336.39	336.90	0.51		0.2	39	8	<10	49	
				6082267	336.90	337.41	0.51		0.4	107	1.426%	<10	32	

DIAMOND DRILL LOG

HOLE No. CM07-02

Property: Crack Moly	NTS:	Claim:	Elevation: 1749 m	Azimuth: 220	Length: 255.12 m	Dip: -65°
Coordinates: 584864 E / 5519267 N	Dip Tests:		Advance:	Depth:	Date Collared: 15/08/07	Date Completed: 18/08/07
Purposes: IP Resistivity	Drilled by: Westcore Drilling		Assays by: Eco Tech		Logged by: M. Miller	

Interval		Rec'y %	Description	Sample No.	Interval		Core Width	Sample Description	Ag ppm	Cu ppm	Mo ppm	W ppm	Zn ppm
From	To				From	To							
0.00	3.50		Casing / Overburden										
3.50	12.50		Granodiorite; some fractured sections; gradational to mafic zones (5%); some K-spar? alteration (red-orange colour); unaltered; cs-gr; massive	6082272	3.50	4.51	1.01		<0.2	18	79	<10	42
				6082273	4.51	5.48	0.97		0.4	17	43	<10	110
				6082274	7.03	8.03	1.00		0.4	128	50	<10	486
				6082275	8.03	9.43	1.40		0.3	13	17	<10	65
				6082276	9.43	10.45	1.02		0.3	29	29	<10	124
				6082277	10.45	11.50	1.05		0.4	67	104	<10	79
				6082278	11.50	12.50	1.00		1.2	680	198	<10	110
12.50	27.32		Altered Granodiorite; altered by fine-grained infiltration of granitic rock	6082279	12.50	13.49	0.99	STANDARD BLANK	1.3	363	226	<10	72
				6082280									
				6082281									
				6082282	13.49	14.49	1.00		0.6	132	68	<10	78
				6082283	14.49	16.41	1.92		0.8	209	117	<10	109
				6082284	16.41	17.41	1.00		0.5	62	117	<10	182
				6082285	17.41	18.38	0.97		0.2	91	109	<10	86
				6082286	18.38	19.30	0.92		2.4	1334	299	10	176
				6082287	19.30	20.30	1.00		0.6	187	106	150	89
				6082288	20.30	22.30	2.00		0.4	108	107	<10	89

DIAMOND DRILL LOG

HOLE No. CM07-02

Interval		Rec'y %	Description	Sample No.	Interval		Core Width	Sample Description	Ag ppm	Cu ppm	Mo ppm	W ppm	Zn ppm
From	To				From	To							
				6082289	22.30	24.30	2.00		0.4	19	115	<10	55
				6082290	25.70	27.32	1.62		0.2	46	139	<10	57
				6082291				STANDARD					
27.32	29.78		Foliated Granodiorite; weakly foliated as defined by biotite flakes; coarse-grained	6082292	27.32	28.80	1.48		<0.2	57	0.052%	<10	54
				6082293	28.80	29.78	0.98		0.5	40	72	<10	48
29.78	41.76		Heterolithic Breccia; consists of angular fragments of granodiorite, quartz porphyry and absorbed granitic "clasts", mo in fx's + qtz veins	6082294	29.78	30.84	1.06		0.6	25	0.114%	10	49
				6082295	30.84	32.84	2.00		0.6	149	170	<10	93
				6082296	34.65	36.68	2.03		0.9	322	161	<10	74
				6082297	37.20	38.71	1.51		1.9	883	168	20	229
				6082298	38.71	41.76	3.05		1.0	375	186	<10	148
41.76	53.95		Altered Granodiorite	6082299	45.81	47.96	2.15		1.2	199	144	<10	59
				6082300	47.96	48.96	1.00		0.6	169	63	<10	76
				6082301	52.95	53.95	1.00		0.7	19	430	<10	58
53.95	61.10		Monolithic Breccia; Granodiorite breccia; fn-gr matrix; silica flooding at top of unit; local qtz veins, tr-<1% mo, cpy	6082302	53.95	55.00	1.05		0.2	85	259	<10	41
				6082303	55.00	57.00	2.00		1.0	451	165	<10	79
				6082304	60.05	61.10	1.05		0.8	106	103	60	102
61.10	78.20		Heterolithic Breccia; mixed granitic clasts	6082305	64.20	65.25	1.05		0.3	77	52	<10	80
				6082306				STANDARD					
				6082307	72.44	73.44	1.00		0.6	224	93	<10	259
				6082308	76.20	77.20	1.00		<0.2	57	323	<10	102
				6082309	77.20	78.20	1.00		0.3	90	147	<10	80

DIAMOND DRILL LOG

HOLE No. CM07-02

Interval		Rec'y %	Description	Sample No.	Interval		Core Width	Sample Description	Ag ppm	Cu ppm	Mo ppm	W ppm	Zn ppm
From	To				From	To							
78.20	82.14		Monolithic Breccia	6082310	78.20	79.20	1.00	STANDARD BLANK	<0.2	87	211	<10	80
				6082311	79.20	80.28	1.08		0.3	70	152	<10	100
				6082312	81.28	82.14	0.86		<0.2	38	199	<10	94
				6082313									
				6082314									
82.14	114.91		Altered Granodiorite	6082315	90.50	91.50	1.00	0.2	58	54	<10	122	
				6082316	91.50	92.60	1.10	0.4	246	113	20	197	
				6082317	92.60	93.81	1.21	<0.2	140	305	10	119	
				6082318	93.81	94.40	0.59	0.4	109	162	<10	235	
				6082319	94.40	95.85	1.45	0.6	339	124	10	344	
				6082320	96.62	97.97	1.35	<0.2	77	0.066%	<10	108	
				6082321	110.00	110.98	0.98	0.8	25	62	<10	65	
				6082322	110.98	111.98	1.00	0.8	71	306	<10	113	
				6082323	113.91	114.91	1.00	0.6	53	145	<10	72	
114.91	129.15		Foliated Granodiorite; foliated; some silicified sections with 2-3 cm qtz veins;	6082324	118.31	119.40	1.09	0.2	68	17	<10	62	
				6082325	120.73	121.83	1.20	0.2	59	39	<10	66	
				6082326	127.32	128.40	1.08	0.2	179	95	<10	72	
				6082327									
129.15	154.50		Mixed Altered Granodiorite and GD Breccia	6082328	129.15	130.15	1.00	0.5	231	0.219%	<10	57	

DIAMOND DRILL LOG

HOLE No. CM07-02

Interval		Rec'y %	Description	Sample No.	Interval		Core Width	Sample Description	Ag ppm	Cu ppm	Mo ppm	W ppm	Zn ppm
From	To				From	To							
			129.70-132.02 m: GD, aphanitic, light grey-white, speckled; qv flooding	6082329	133.20	134.19	0.99		0.4	245	222	<10	30
			132.02-138.51 m: QP, slight chill margins; contacts @ 45° to CA	6082330	145.77	146.77	1.00		<0.2	98	123	<10	95
			138.51-149.85 m: GD breccia, rare mo partings and qtz veins; @ 148.85 m is 40 cm broken and weathered core	6082331	153.50	154.50	1.00		1.2	530	120	<10	186
154.50	218.54		Heterolithic Breccia; small QP dykes in altered zones (silicia) minor py, cpy	6082332	154.50	155.50	1.00	STANDARD	1.0	393	46	<10	125
				6082333	155.50	156.53	1.03		0.6	297	0.077%	<10	94
				6082334	168.81	169.81	1.00		1.4	544	23	<10	117
			6082335	169.81	170.81	1.00	1.8		834	32	<10	105	
			6082336	170.81	171.81	1.00	1.2		608	324	<10	140	
			173.00-174.50 m: weathered, oxidized py	6082337	171.81	173.35	1.54		0.4	126	63	<10	67
				6082338									
				6082339	181.97	183.00	1.03		2.4	816	108	<10	126
			180.20-182.10 m: some alteration to nepheline	6082340	183.00	184.00	1.00		0.5	249	176	<10	69
				6082341	190.50	191.84	1.34		3.0	1298	20	<10	111
				6082342	193.43	194.43	1.00		3.4	1719	9	<10	209
				6082343	198.42	199.42	1.00		1.6	716	22	10	159
				6082344	199.42	200.42	1.00		2.1	1080	107	<10	137
				6082345	203.50	204.50	1.00		1.9	809	204	<10	137
				6082346	207.35	208.35	1.00		4.4	1304	75	<10	194
6082347	209.38	210.46		1.08	0.4	99	42	<10	99				
6082348	210.46	211.46		1.00	0.4	184	174	<10	113				

DIAMOND DRILL LOG

HOLE No. CM07-03

Property: Crack Moly	NTS:	Claim:	Elevation: 1681	Azimuth: 180	Length: 323.70 m	Dip: -65°
Coordinates: 585151 E / 5519451 N	Dip Tests:		Advance:	Depth:	Date Collared: 22/08/07	Date Completed: 26/08/07
Purposes: IP Conductor	Drilled by: Westcore Drilling		Assays by: Echo Tech		Logged by: M. Miller	

Interval		Rec'y %	Description	Sample No.	Interval		Core Width	Sample Description	Ag ppm	Cu ppm	Mo ppm	W ppm	Zn ppm
From	To				From	To							
0.00	1.25		Casing / Overburden										
1.25	26.10		Hornblende-Biotite; with diorite sections > 2 m wide; cs-gr. mo in qtz veins, interstitially, and as partings; unit has clasts of GD, diorite, QP, and bio-rich granitic clasts	17401	1.25	2.45	1.20	STANDARD	<0.2	42	0.320%	<10	103
				17402	2.45	3.55	1.10		0.6	40	0.102%	<10	89
				17403	3.55	4.65	1.10		<0.2	67	172	<10	98
				17404	4.65	5.70	1.05		<0.2	94	209	<10	163
				17405	5.70	6.60	0.90		<0.2	54	0.055%	<10	71
				17406	6.60	7.60	1.00		<0.2	73	328	<10	91
				17407	7.60	8.60	1.00		<0.2	101	361	<10	118
				17408	8.60	9.60	1.00		<0.2	121	446	<10	65
				17409	9.60	10.60	1.00		<0.2	35	318	<10	66
				17410	10.60	11.65	1.05		<0.2	46	252	<10	63
				17411									
				17412	11.65	12.69	1.04		<0.2	52	76	<10	52
				17413	12.69	14.29	1.60		<0.2	103	259	<10	77
				17414	14.29	15.39	1.10		0.2	139	401	<10	134
				17415	15.39	17.00	1.61		0.4	81	59	<10	160
				17416	17.00	18.38	1.38		0.2	29	400	<10	77
				17417	18.38	19.38	1.00		<0.2	34	0.081%	<10	48

DIAMOND DRILL LOG

HOLE No. CM07-03

Interval		Rec'y %	Description	Sample No.	Interval		Core Width	Sample Description	Ag ppm	Cu ppm	Mo ppm	W ppm	Zn ppm	
From	To				From	To								
				17418	19.38	20.42	1.04		0.2	76	0.108%	<10	101	
				17419	20.42	21.92	1.50		<0.2	78	33	<10	114	
				17420	21.92	22.92	1.00		<0.2	55	84	<10	87	
				17421	22.92	23.92	1.00		<0.2	12	161	<10	59	
				17422	23.92	24.92	1.00		<0.2	36	75	<10	52	
				17423	24.92	26.10	1.18		<0.2	113	61	<10	48	
26.10	36.30		Quartz Porphyry; abrupt contact @ 60° to CA; upper 9 m weakly altered with Fe-stain; competent; rare mo partings; aphanitic; leucocratic grey-blue	17424	26.10	27.10	1.00	STANDARD	0.3	88	58	<10	68	
				17425										
				17426	29.45	30.45	1.00		<0.2	41	355	<10	125	
				17427	30.45	31.45	1.00		<0.2	23	483	<10	55	
				17428	32.06	33.09	1.03		0.2	49	230	<10	71	
36.30	50.78		Granodiorite Breccia	17429	36.20	37.20	1.00	STANDARD	0.3	119	164	<10	240	
			36.30-41.71 m: has dioritic sections	17430	37.20	38.15	0.95		<0.2	69	0.196%	<10	48	
			41.71-50.78 m: has qtz veins with mo	17431	38.15	39.15	1.00		<0.2	83	0.459%	<10	88	
				17432	39.15	40.15	1.00		<0.2	39	0.239%	<10	47	
				17433	40.15	41.17	1.02		<0.2	78	72	<10	29	
				17434	42.52	43.52	1.00		0.2	38	73	<10	71	
				17435	43.52	44.52	1.00		<0.2	39	119	<10	72	
				17436										
				17437	45.50	46.50	1.00		3	1523	0.061%	<10	129	
				17438	46.50	47.70	1.20		<0.2	48	0.061%	<10	68	

DIAMOND DRILL LOG

HOLE No. CM07-03

Interval		Rec'y %	Description	Sample No.	Interval		Core Width	Sample Description	Ag ppm	Cu ppm	Mo ppm	W ppm	Zn ppm
From	To				From	To							
				17439				STANDARD					
				17440				BLANK					
50.78	54.60		Hornblende-Biotite; traces of mo and 1 qtz vein with cs mo	17441	50.13	51.17	1.04		<0.2	157	422	<10	56
				17442	51.17	52.17	1.00		<0.2	83	493	<10	61
				17443	52.17	53.06	0.89		<0.2	41	0.189%	<10	90
				17444	53.06	54.10	1.04		<0.2	105	0.097%	<10	200
54.60	57.00		Quartz Porphyry; has 1 po bleb, LC is qtz vein with cs-gr mo	17445	54.10	55.10	1.00		0.4	190	0.092%	<10	275
				17446	56.41	57.00	0.59		<0.2	29	0.201%	<10	40
57.00	90.36		Hornblende-Biotite with Diorite Sections; some sections > 1% mo as dissm and qtz veins; mo stronger towards bottom of unit; LC weathered and intermixed	17447	57.00	58.14	1.14		<0.2	32	0.083%	<10	59
				17448	58.14	59.20	1.06		<0.2	55	447	<10	86
				17449	59.20	60.20	1.00		<0.2	43	0.050%	<10	92
				17450	60.20	61.57	1.37		<0.2	25	428	<10	70
				17451				STANDARD					
				17452	61.57	62.80	1.23		<0.2	58	146	<10	70
				17453	62.80	63.77	0.97		<0.2	47	432	<10	51
				17454	63.77	64.77	1.00		<0.2	33	52	<10	55
				17455	64.77	65.84	1.07		<0.2	29	0.058%	<10	60
				17456	65.84	66.84	1.00		<0.2	36	0.112%	<10	93
				17457	66.84	68.31	1.47		<0.2	53	177	<10	72
				17458	68.31	69.31	1.00		<0.2	56	174	<10	74
				17459	69.31	70.28	0.97		<0.2	92	0.129%	<10	72

DIAMOND DRILL LOG

HOLE No. CM07-03

Interval		Rec'y %	Description	Sample No.	Interval		Core Width	Sample Description	Ag ppm	Cu ppm	Mo ppm	W ppm	Zn ppm
From	To				From	To							
				17460	70.28	71.45	1.17		<0.2	83	0.082%	<10	514
				17461	71.45	72.61	1.16		<0.2	19	0.067%	<10	173
				17462	72.61	73.88	1.27		<0.2	39	0.078%	<10	70
				17463	75.29	76.35	1.06		<0.2	50	416	<10	200
				17464	76.35	77.37	1.02		<0.2	62	0.231%	<10	157
				17465	77.37	78.33	0.96		<0.2	38	0.074%	<10	63
				17466	78.33	79.33	1.00		<0.2	59	0.078%	<10	54
				17467				STANDARD					
				17468	79.33	80.28	0.95		<0.2	58	0.284%	<10	28
				17469	80.28	81.17	0.89		<0.2	110	0.297%	<10	76
				17470	81.17	81.96	0.79		<0.2	61	29	<10	30
				17471	81.96	82.98	1.02		<0.2	162	217	<10	45
				17472	82.98	83.98	1.00		<0.2	87	288	<10	62
				17473				BLANK					
				17474	83.98	85.00	1.02		<0.2	87	87	<10	30
				17475	85.00	86.10	1.10		<0.2	84	462	<10	61
				17476	86.10	87.48	1.38		<0.2	47	0.099%	<10	50
				17477	87.48	88.53	1.05		<0.2	77	245	<10	50
				17478				STANDARD					
				17479	88.53	89.53	1.00		<0.2	44	0.183%	<10	35
				17480	89.53	90.53	1.00		<0.2	47	36	<10	25

DIAMOND DRILL LOG

HOLE No. CM07-03

Interval		Rec'y %	Description	Sample No.	Interval		Core Width	Sample Description	Ag ppm	Cu ppm	Mo ppm	W ppm	Zn ppm
From	To				From	To							
90.36	102.15		Quartz Porphyry; solid, competent core; green-grey-bluish colour; aphanitic to porphyritic with minor py, cpy; LC weakly mineralized	17481				STANDARD					
				17482	101.97	102.72	0.75		<0.2	33	88	<10	38
102.15	112.00		Hornblende-Biotite; mixed assemblage with intermixed dioritic intervals; becomes more dioritic towards bottom of interval	17483	102.72	103.70	0.98		<0.2	21	0.075%	<10	60
				17484	103.70	104.55	0.85		<0.2	15	206	10	65
				17485	104.55	105.55	1.00		<0.2	44	179	10	85
				17486	105.55	106.55	1.00		<0.2	54	225	<10	95
				17487	106.55	107.95	1.40		<0.2	78	426	<10	159
				17488	107.95	108.95	1.00		<0.2	60	210	<10	169
				17489	109.88	111.11	1.23		<0.2	51	98	<10	32
112.00	120.45		Granodiorite Breccia / Quartz Porphyry; interbedded lithologies; more GD than granitic; contains disseminated mo always proximal to qtz veins; most qtz veins with mo, veins 1 mm to 5 cm wide	17490	112.50	114.60	2.10		<0.2	83	155	<10	59
				17491	114.60	115.68	1.08		<0.2	55	323	<10	19
				17492	115.68	116.77	1.09		0.2	68	82	<10	16
				17493	116.77	117.82	1.05		0.2	51	161	<10	22
				17494	117.82	118.96	1.14		<0.2	66	258	<10	23
120.45	144.65		Hornblende Biotite; unit has qtz veins with strong mo	17495				STANDARD					
				17496	124.69	125.77	1.08		<0.2	40	24	<10	56
				17497	127.63	130.10	2.47		<0.2	48	164	<10	23
				17498	132.73	133.69	0.96		<0.2	110	213	<10	113
				17499	133.69	134.89	1.20		1	33	13	<10	53
				17500	134.89	135.95	1.06		0.2	145	123	<10	51
				17501	135.95	136.90	0.95		<0.2	77	0.069%	<10	45

DIAMOND DRILL LOG

HOLE No. CM07-03

Interval		Rec'y %	Description	Sample No.	Interval		Core Width	Sample Description	Ag ppm	Cu ppm	Mo ppm	W ppm	Zn ppm
From	To				From	To							
				17502	136.90	137.94	1.04		<0.2	73	234	<10	31
				17503	137.94	139.22	1.28		<0.2	62	74	<10	42
				17504	139.22	140.22	1.00		<0.2	68	147	<10	112
				17505	140.22	141.24	1.02		0.2	84	0.049%	<10	35
				17506	141.24	142.16	0.92		<0.2	82	386	<10	45
				17507	142.16	142.65	0.49		<0.2	95	257	<10	51
				17508	142.65	143.16	0.51		<0.2	93	3.320%	<10	71
				17509				BLANK					
				17510				STANDARD					
				17511	143.16	143.66	0.50		0.8	533	0.988%	<10	79
144.65	211.10		Intermixed Hornblende-Biotite / Qtz Porphyry; intermixed lithologies with local sections of GD breccia; local qtz veins have mo and sericite	17512	143.66	144.73	1.07		1.2	198	476	<10	52
				17513	144.73	145.77	1.04		<0.2	41	218	<10	33
				17514	145.77	146.78	1.01		0.2	100	0.314%	<10	106
				17515	146.78	147.70	0.92		<0.2	36	0.122%	<10	25
				17516	147.70	148.70	1.00		<0.2	41	0.064%	<10	37
				17517	148.70	149.69	0.99		0.2	64	0.049%	<10	44
				17518	149.69	150.64	0.95		0.2	33	168	<10	40
				17519	150.64	151.63	0.99		<0.2	38	93	<10	41
				17520				STANDARD					
				17521	151.63	152.65	1.02		<0.2	94	329	<10	56
				17522	152.65	153.65	1.00		<0.2	44	110	<10	83

DIAMOND DRILL LOG

HOLE No. CM07-03

Interval		Rec'y %	Description	Sample No.	Interval		Core Width	Sample Description	Ag ppm	Cu ppm	Mo ppm	W ppm	Zn ppm
From	To				From	To							
				17523	153.65	154.53	0.88		<0.2	89	117	<10	95
				17524	154.53	155.63	1.10		1.3	741	0.318%	<10	74
				17525				BLANK					
				17526	155.63	156.58	0.95		0.3	183	460	<10	28
				17527	156.58	157.50	0.92		1.3	121	471	<10	55
				17528	157.50	158.60	1.10		<0.2	39	366	<10	52
				17529	164.84	165.84	1.00		0.4	106	0.073%	<10	83
				17530				STANDARD					
				17531	165.84	166.79	0.95		0.8	256	440	<10	223
				17532	166.79	168.01	1.22		<0.2	43	23	<10	26
				17533	168.01	169.04	1.03		<0.2	65	318	<10	50
				17534	169.04	170.16	1.12		0.4	66	196	<10	34
				17535	172.88	173.88	1.00		0.2	61	250	<10	57
				17536	173.88	174.85	0.97		<0.2	50	27	<10	225
				17537	186.62	187.71	1.09		<0.2	108	91	<10	64
				17538	187.71	188.90	1.19		<0.2	304	197	<10	44
				17539				STANDARD					
				17540				BLANK					
				17541	190.60	191.60	1.00		<0.2	23	195	<10	50
				17542	191.60	192.68	1.08		<0.2	86	78	<10	35
				17543	194.16	195.25	1.09		<0.2	94	228	<10	73

DIAMOND DRILL LOG

HOLE No. CM07-03

Interval		Rec'y %	Description	Sample No.	Interval		Core Width	Sample Description	Ag ppm	Cu ppm	Mo ppm	W ppm	Zn ppm
From	To				From	To							
				17544	195.25	196.35	1.10		0.6	387	163	<10	37
				17545	196.35	197.58	1.23		<0.2	36	129	<10	46
				17546	197.58	198.95	1.37		<0.2	101	350	<10	72
				17547	202.13	203.15	1.02		<0.2	125	318	<10	287
				17548	203.15	204.10	0.95		<0.2	61	0.209%	<10	80
211.10	273.20		Granodiorite Breccia; mafic groundmass, broken core from 221.00-224.00 metres	17549	210.07	211.25	1.18		0.2	160	69	<10	173
				17550	211.25	212.32	1.07		<0.2	28	457	<10	112
				17551				STANDARD					
				17552	212.32	213.28	0.96		<0.2	109	400	<10	77
				17553	213.28	214.39	1.11		<0.2	64	42	<10	71
				17554	214.39	215.39	1.00		<0.2	239	87	<10	73
				17555	215.39	216.52	1.13		<0.2	134	90	<10	85
				17556	231.41	232.38	0.97		<0.2	47	218	<10	63
				17557	232.38	233.45	1.07		0.4	311	0.050%	<10	55
				17558	233.45	234.50	1.05		0.2	210	0.053%	<10	59
				17559	237.43	238.42	0.99		<0.2	37	103	<10	76
				17560	238.42	239.88	1.46		1.2	122	58	<10	139
				17561				STANDARD					
				17562	239.88	241.06	1.18		<0.2	31	126	<10	78
				17563	241.06	242.30	1.24		<0.2	285	23	<10	92
				17564	243.06	244.16	1.10		<0.2	119	24	<10	87

DIAMOND DRILL LOG

HOLE No. CM07-04

Property: Crack Moly	NTS:	Claim:	Elevation: 1658 m	Azimuth: 180°	Length: 114.91 m	Dip: -70°
Coordinates: 585324 E / 5519548 N	Dip Tests:		Advance:	Depth:	Date Collared: 28/08/07	Date Completed: 29/08/07
Purposes: IP Anomaly	Drilled by: Westcore Drilling		Assays by: Echo Tech		Logged by: Wesley Raven	

Interval		Rec'y %	Description	Sample No.	Interval		Core Width	Sample Description	Ag ppm	Cu ppm	Mo ppm	W ppm	Zn ppm
From	To				From	To							
0.00	1.00		Casing / Overburden										
1.00	2.25		Granodiorite; massive + homogeneous, biotite porphyritic										
2.25	7.75		Quartz Porphyry; unconformable upper contact, LC at 30° CA; minor vuggy qtz veining; minor GD inclusions; wk iron staining										
7.75	15.33		Granodiorite (Massive); as 1.00-2.25 m; minor qtz veins, no mo	17571	14.33	15.33	1.00		0.8	518	82	<10	54
15.33	24.14		Granodiorite (Foliated); rare qtz veins; tr bo, py, po, cpy	17572	15.33	16.35	1.02		<0.2	18	9	<10	26
				17573	21.80	22.80	1.00		<0.2	66	95	<10	32
21.14	65.20		Quartz Porphyry; UC sharp @ 10° to CA; at 32 m is siliceous zone with <1% py, tr mo	17574	39.37	40.63	2.26		<0.2	28	132	<10	44
				17575	40.63	41.63	1.00		<0.2	18	24	<10	30
				17576	47.20	48.10	0.90		0.2	207	265	<10	52
				17577	48.10	49.05	0.95		<0.2	35	8	<10	71
				17578	49.05	50.05	1.00		<0.2	37	99	<10	39
				17579	50.05	50.90	0.85		<0.2	21	126	<10	20
				17580	50.90	51.88	0.98		0.2	38	232	<10	26
				17581	51.88	52.90	1.02		0.2	90	194	<10	64
			17582	59.56	60.86	1.30		0.4	257	106	<10	96	

DIAMOND DRILL LOG

HOLE No. CM07-05

Property: Crack Moly	NTS:	Claim:	Elevation: 1676 m	Azimuth: 180°	Length: 320.95 m	Dip: -55°
Coordinates: 584998 E / 5519417 N	Dip Tests:		Advance:	Depth:	Date Collared: 30/08/07	Date Completed: 09/09/07
Purposes: IP Chargeability	Drilled by: Westcore Drilling		Assays by: Eco Tech		Logged by: M. Miller / W. Raven	

Interval		Rec'y %	Description	Sample No.	Interval		Core Width	Sample Description	Ag ppm	Cu ppm	Mo ppm	W ppm	Zn ppm
From	To				From	To							
0.00	2.18		Casing/Overburden										
2.18	8.00		Massive Biotite Granodiorite; weak Fe stain, broken										
8.00	39.50		Quartz Porphyry; altered, green, soft, brecciated, calcite altered at 14.44 m, broken in places, 2.20 m of core washed away from 29.00-32.00 m; mo in f.g. qtz veins	17601	34.01	35.13	1.12	gd/qp, v. broken, tr mo, at contact	0.3	108	0.111%	<10	46
				17602	35.13	36.19	1.06	less broken altn	<0.2	51	53	<10	83
				17603	36.19	37.19	1.00		<0.2	16	50	<10	47
				17604	37.19	38.05	0.86		<0.2	27	196	<10	42
				17605	38.05	39.03	0.98	alt, ep gd, 10 cm qv with mo	<0.2	36	0.349%	<10	48
				17606	39.03	40.05	1.02	alt gd, vf.g. qtz vein with mo	<0.2	77	180	<10	48
39.50	131.45		Grandodiorite 49.70-54.36 m: alt gd, qp, 78-79.8 msv, sharp contact lower 45% tca, upper alt g.d. in 5 cm q.v., mo tr	17607				STANDARD					
				17608	40.05	41.05	1.00		<0.2	34	98	<10	68
				17609	41.05	42.05	1.00		<0.2	19	69	<10	48
				17610	42.05	43.10	1.05	gd, minor q.v. with Mo	<0.2	22	181	<10	83
				17611	50.90	51.90	1.00	alt GD, mo in alt gd, sil, fe stain	0.2	25	437	<10	115
				17612	51.90	52.90	1.00	alt gd, 2 x 5 cm q.v., tr Mo	<0.2	26	216	<10	44
				17613	52.90	62.19	0.99	gd	<0.2	19	76	<10	50
				17614	62.19	63.25	1.00	gd, 5 cm gv. no v. mo	0.2	20	19	<10	49

DIAMOND DRILL LOG

HOLE No. CM07-05

Interval		Rec'y %	Description	Sample No.	Interval		Core Width	Sample Description	Ag ppm	Cu ppm	Mo ppm	W ppm	Zn ppm
From	To				From	To							
				17615	63.25	64.35	1.10	q.v, tr mo	<0.2	41	149	<10	47
				17616	66.91	68.09	1.18		0.2	27	72	<10	72
				17617	68.09	69.09	1.00		<0.2	18	166	<10	74
				17618	69.09	70.11	1.02		<0.2	69	388	<10	52
				17619	71.88	72.85	0.97		<0.2	42	362	<10	48
				17620	72.85	73.85	1.00		<0.2	31	454	<10	43
				17621	73.85	74.85	1.00		<0.2	24	0.880%	<10	42
				17622	74.85	75.85	1.00		<0.2	19	0.060%	<10	42
				17623	75.85	76.85	1.00		<0.2	21	371	<10	43
				17624	76.85	77.37	0.52		<0.2	66	0.091%	<10	40
				17625				STANDARD					
				17626	80.38	81.38	1.00		<0.2	37	0.079%	<10	43
				17627	81.38	82.33	0.95		<0.2	41	23	<10	43
			82.48 m: 14 cm white q.v.	17628	82.33	83.25	0.92		<0.2	49	111	<10	50
				17629	84.57	85.54	0.97		<0.2	121	491	<10	73
				17630	85.54	86.34	0.80		<0.2	82	183	<10	46
			86.0-87.55 m: grn alt gd q.v. with c Mo calcic alt	17631	86.54	87.48	1.14		0.4	50	183	<10	49
				17632	87.48	88.48	1.00	tr mo + po as dissm	<0.2	13	130	<10	47
			90.50-92.50 m: 1 mo-qtz vein with cs. gr. mo blebs	17633	88.48	90.50	2.02	tr-0.5% mo, tr po	<0.2	28	63	<10	49
			92.50-94.50 m: 3 mm qtz-mo vein @ 30° to CA	17634	90.50	92.50	2.00	tr mo	0.4	21	390	<10	44
			94.50-96.50 m: 3 x 1 mm mo veins	17635	92.50	94.50	2.00	tr mo	<0.2	23	89	<10	53

DIAMOND DRILL LOG

HOLE No. CM07-05

Interval		Rec'y %	Description	Sample No.	Interval		Core Width	Sample Description	Ag ppm	Cu ppm	Mo ppm	W ppm	Zn ppm
From	To				From	To							
			96.50-98.50 m: 1 cm qtz vein with cs-gr mo on margins	17636	94.50	96.50	2.00	tr mo	0.4	39	251	<10	48
			98.50-100.50 m: 2-3 mm mo vein @ 35° to CA with	17637	96.50	98.50	2.00	tr mo, cpy, po	0.2	30	378	<10	51
			100.50-102.50 m: qtz-mo 1 mm, veinlets x 3 + diss	17638	98.50	100.50	2.00	tr mo, tr po + cpy	0.2	29	95	<10	55
			102.50-104.50 m: qtz-mo vein, 2 cm with cpy + po as cs blebs	17639	100.50	102.50	2.00	tr-0.5% mo, tr po	0.2	31	58	<10	51
				17640	102.50	104.50	2.00	tr-0.5% mo, tr po, cpy	0.6	286	86	<10	61
			104.50-106.50 m: vein as above to 104.50 m, minor fx-fill mo at 75° to CA	17641	104.50	106.50	2.00	tr mo	<0.2	147	181	<10	51
				17642	106.50	108.30	2.00	tr mo	<0.2	32	25	<10	53
			106.50-108.50 m: 2-3 mm mo vein @ 37° to CA	17643	108.30	110.50	2.00	tr mo	1.4	52	256	<10	63
			108.50-110.50 m: qtz-mo veins, 1 mm x 3	17644				STANDARD					
			110.50-112.50 m: 2-3 cm qtz vein with clots of mo + cpy	17645	110.50	112.50	2.00	tr-0.5% mo, tr cpy	0.6	433	130	<10	54
			114.50-116.50 m: mo veinlets @ 25° to CA, qtz-mo veinlets @ 20° to CA	17646	112.50	114.50	2.00	tr mo	<0.2	19	349	<10	72
				17647	114.50	116.50	2.00	tr-0.5% mo	<0.2	22	89	<10	58
			117.96-118.56 m: sausseritized with grey silica flooding for 10 cm above fault zone at 55° to CA	17648	116.50	118.50	2.00	tr-0.5% mo	<0.2	49	209	<10	53
				17649	118.50	120.50	2.00	tr mo	<0.2	28	86	<10	52
			119.77-119.81 m: qtz vein with cs-gr blebs of mo + cpy in alteration halo around vein margins	17650	120.50	122.50	2.00	0.5% mo	<0.2	24	201	<10	52
				17651	122.50	124.50	2.00	tr mo	<0.2	33	23	<10	46
			120.50-122.50 m: qtz-mo veinlets @ 20° to CA, mo veins @ 30° to CA	17652	124.50	126.50	2.00	tr mo	<0.2	23	41	<10	55
				17653	126.50	128.50	2.00	tr mo	<0.2	28	9	<10	57
			124.50-126.50 m: minor mo veinlets, 1 mm wide @ 20° to 65° to CA; pale green QFP @ 126.17-126.53 m, sharp contacts @ 20° to CA	17654	128.50	130.50	2.00	nil-tr mo	<0.2	46	58	<10	57
				17655	130.50	131.45	0.95	tr mo	0.2	40	61	<10	75

DIAMOND DRILL LOG

HOLE No. CM07-05

Interval		Rec'y %	Description	Sample No.	Interval		Core Width	Sample Description	Ag ppm	Cu ppm	Mo ppm	W ppm	Zn ppm
From	To				From	To							
				17675	156.00	157.50	1.50	tr mo	<0.2	46	206	<10	49
				17676	157.50	159.00	1.50	tr-0.5% mo	<0.2	40	152	<10	55
				17677	159.00	160.50	1.50	tr mo	0.2	29	178	<10	39
				17678	160.50	162.00	1.50	tr mo	<0.2	35	123	<10	47
				17679	162.00	163.50	1.50	tr mo	<0.2	28	130	<10	38
				17680	163.50	165.00	1.50	tr mo, tr cpy	<0.2	81	296	<10	47
				17682	165.00	166.50	1.50	tr mo	<0.2	32	91	<10	42
				17682	166.50	168.00	1.50	tr-0.5% mo	0.2	37	0.062%	<10	41
				17683	168.00	169.50	1.50	tr-0.5% mo	<0.2	23	115	<10	42
				17684	169.50	171.00	1.50	tr mo	<0.2	39	156	<10	46
				17685	171.00	172.50	1.50	tr-0.5% mo	0.4	53	172	<10	72
				17686	172.50	174.00	1.50	tr mo	2.2	45	38	<10	51
				17687	174.00	175.78	1.78	tr-0.5% mo	1.0	40	178	<10	54
175.78	227.94		Quartz Porphyry ± Breccia; predominantly mottled grey colour, locally pale green; highly silicified throughout; locally contains some GD clasts or black feldspar porphyry and a black bio-chl altn; minor mo present throughout as pure mo veinlets and qtz veins with mo more common along vein margins; gradational unit contacts; locally unit is strongly fractured as noted	17688	175.78	177.62	1.84	tr mo	<0.2	38	9	<10	44
				17689	177.62	179.46	1.84	tr mo	<0.2	39	3.644%	<10	106
				17690	179.46	181.30	1.84	tr mo	<0.2	23	55	<10	82
				17691	181.30	183.35	2.05	tr-0.5% mo	<0.2	119	0.083%	<10	109
				17692	183.35	185.40	2.05	tr-0.5% mo	0.4	52	0.197%	<10	84
			181.30-185.40 m: pale green QP that has local ep-carb altn; from 182.50-183.17 is qtz vein with cs-gr clots of mo	17693	185.40	187.50	2.10	tr-0.5% mo	<0.2	33	123	<10	45
				17694	187.50	189.50	2.00	tr mo	<0.2	24	204	<10	59
				17695	189.50	191.50	2.00	tr mo	<0.2	30	35	<10	48

DIAMOND DRILL LOG

HOLE No. CM07-05

Interval		Rec'y %	Description	Sample No.	Interval		Core Width	Sample Description	Ag ppm	Cu ppm	Mo ppm	W ppm	Zn ppm
From	To				From	To							
				17696	191.50	193.50	2.00	tr mo	0.4	23	9	<10	41
				17697				STANDARD					
			194.00-208.70 m: moderately to strongly broken and fractured	17698	193.50	195.50	2.00	tr mo	<0.2	35	199	<10	62
				17699	195.50	197.50	2.00	tr-0.5% mo	0.4	55	29	<10	76
			195.50-197.50 m: 1-4 mm wide qtz-mo veinlets @ 15° to CA	17700	197.50	199.50	2.00	tr-0.5% mo	0.6	27	406	<10	39
				17701	199.50	201.50	2.00	tr-0.5% mo	0.2	27	19	<10	50
				17702	201.50	203.50	2.00	tr mo	<0.2	23	121	<10	43
				17703	203.50	205.50	2.00	tr-0.5% mo, tr cpy, py	0.2	25	67	<10	60
				17704	205.50	207.50	2.00	tr-0.5% mo, tr cpy, py	0.2	43	45	<10	104
			209.50-211.50 m: veinlets at 40° + 60° to CA	17705	207.50	209.50	2.00	tr mo	0.2	44	58	<10	83
				17706	209.50	211.50	2.00	tr mo, tr py, cpy	<0.2	45	63	<10	46
				17707	211.50	213.50	2.00	tr mo	0.2	43	32	<10	56
				17708	213.50	215.50	2.00	tr mo	<0.2	23	7	<10	52
				17709	215.50	217.50	2.00	tr mo	0.4	30	7	<10	64
			217.77-227.94 m: pale green and aphanitic	17710	217.50	219.50	2.00	tr mo	<0.2	20	117	<10	41
				17711	219.50	221.50	2.00	tr-0.5% mo	<0.2	26	19	<10	39
				17712	221.50	223.50	2.00	tr-0.5% mo	<0.2	22	136	<10	51
				17713	223.50	225.50	2.00	tr-0.5% mo	0.2	120	60	<10	74
				17714	225.50	227.50	2.00	tr-0.5% mo	0.4	65	12	<10	54
				17715	227.50	229.50	2.00	nil-tr mo	0.4	46	18	<10	54

DIAMOND DRILL LOG

HOLE No. CM07-05

Interval		Rec'y %	Description	Sample No.	Interval		Core Width	Sample Description	Ag ppm	Cu ppm	Mo ppm	W ppm	Zn ppm
From	To				From	To							
227.94	273.36		<p>Grandodiorite; medium to coarse grained, massive and homogenous, hornblende altering to biotite and phlogopite; occasionally has weak fabric by alignment of biotite crystals; upper contact is gradational; has very minor mo veinlets but of insufficient density</p> <p>259.44-273.36 m: foliated GD at 45°-60° to CA; whole interval looks weakly brecciated</p> <p>264.69-265.48 m: 20% qtz flooding with very weak mo</p> <p>272.46-272.90 m: grey qtz-porphyry</p>	17716	229.50	231.50	2.00	nil-tr mo	0.4	180	60	<10	62
273.36	278.24		Quartz Porphyry; as previously described, pale green colour; has qtz-mo veins from 1-10 mm wide @ 15°-25° to CA, qtz >> mo; contacts are gradational	17717	273.36	274.58	1.22	tr-0.5% mo	<0.2	58	13	<10	75
				17718	274.58	275.80	1.22	tr-0.5% mo	0.4	68	194	<10	53
				17719	275.80	277.02	1.22	tr mo	0.4	35	57	<10	88
				17720	277.02	278.24	1.22	tr mo	0.2	62	28	<10	136
278.24	296.71		<p>Quartz Diorite (altered); weakly foliated at ~60° to CA; has biotite alteration throughout as veins parallel to fol. and anastomosing irregular masses with qtz; slight greenish tint due to sausseritization; very minor molybdenite, py + po</p> <p>279.85-280.87 m: broken qtz vein fragments with small blebs of mo, ~20% veining in interval</p>	17721				STANDARD					
				17722	278.24	279.85	1.61	tr mo	0.2	98	166	<10	93
				17723	279.85	280.87	1.02	tr mo	<0.2	85	183	<10	66
				17724	280.87	282.57	1.70	tr mo	0.2	36	50	<10	74
				17725	282.57	284.50	1.93	tr mo, po, py	0.2	160	215	<10	89
				17726	284.50	286.50	2.00	tr mo, po, py	0.2	84	162	<10	118
				17727	286.50	288.50	2.00	tr mo, tr po	0.2	269	175	<10	810
				17728	288.50	290.50	2.00	tr-0.5% mo, 1% py	0.4	98	86	<10	230
				17729	290.50	292.50	2.00	tr mo, 1% py	0.4	134	347	<10	239

DIAMOND DRILL LOG

HOLE No. CM07-06

Property: Crack Moly	NTS:	Claim:	Elevation: 1677 m	Azimuth: n/a	Length: 212.14 m	Dip: -90
Coordinates: 584998 E / 5519418 N	Dip Tests:		Advance:	Depth:	Date Collared: 05/09/07	Date Completed: 09/09/07
Purposes: IP Conductor	Drilled by: Westcore Drilling		Assays by: Eco Tech		Logged by: Wesley Raven	

Interval		Rec'y %	Description	Sample No.	Interval		Core Width	Sample Description	Ag ppm	Cu ppm	Mo ppm	W ppm	Zn ppm
From	To				From	To							
0.00	1.52		Casing / Overburden										
1.52	9.55		Granodiorite; massive and homogeneous; cs-gr; lightly to moderately broken + fractured with fairly strong iron oxide staining, especially on fractures; minor qtz veinlets with mo flecks 3.50-4.50 m: broken and fractured 4.50 m: barren qtz veins at 10° to CA cut by mo-bearing veins @ 60°-70° to CA 6.67-6.88 m: qtz veins with cs-gr py + cpy and mo blebs, very rusty veining	17733	1.52	2.50	0.98	tr mo	0.2	16	118	<10	47
				17734	2.50	3.50	1.00	tr mo, tr py	<0.2	43	0.076%	<10	49
				17735	3.50	4.50	1.00	tr mo, tr py	0.2	24	35	<10	51
				17736	4.50	5.50	1.00	tr-0.5% mo, tr py	<0.2	16	236	<10	41
				17737	5.50	6.50	1.00	tr-0.5% mo, tr py	<0.2	49	244	<10	48
				17738	6.50	7.50	1.00	tr-0.5% each mo, cpy; 1% py, tr mal	0.8	734	81	<10	67
				17739	7.50	8.50	1.00	tr-0.5% mo, tr py + cpy	<0.2	53	0.052%	<10	49
				17740	8.50	9.55	1.05		0.2	57	123	<10	51
9.55	11.68		Quartz Porphyry; white colour, v. fine-grained; shattered and broken throughout with strong iron oxide and weaker manganese oxide staining on fractures; UC broken, LC sharp but irregular at ~30° to CA 11.68 m: limit of oxidation	17741	9.55	10.60	1.05	tr mo + sulph	<0.2	59	27	<10	35
				17742	10.60	11.68	1.08	tr mo + sulph	0.2	136	59	<10	35
11.68	39.83		Granodiorite; as 1.52-9.55 m but is below limit of oxidation except for local fracture zones; weak veining (qtz ± mo); veining strongest near upper contact 18.10 m: 3 mm wide cpy-py-mo vein	17743	11.68	13.00	1.32	tr-0.5% mo	<0.2	70	47	<10	57
				17744	13.00	14.50	1.50	tr mo	<0.2	46	24	<10	101
				17745	14.50	16.00	1.50	tr mo	<0.2	22	18	<10	95
				17746	16.00	17.50	1.50	tr mo	<0.2	52	41	<10	68

DIAMOND DRILL LOG

HOLE No. CM07-06

Interval		Rec'y %	Description	Sample No.	Interval		Core Width	Sample Description	Ag ppm	Cu ppm	Mo ppm	W ppm	Zn ppm
From	To				From	To							
				17747	17.50	19.00	1.50	tr mo, tr cpy, py	1.2	529	22	<10	119
				17748	19.00	20.50	1.50	tr mo, tr cpy, py	<0.2	31	242	<10	157
				17749	20.50	22.00	1.50	tr-0.5% mo	<0.2	35	378	<10	112
			23.60-23.90 m: altered and sausseritized with moderate qtz-mo veining and mo on fx surfaces both at 50°-60° to CA	17750	22.00	23.50	1.50	tr-0.5% mo	<0.2	34	151	<10	49
				17751	23.50	25.00	1.50	tr-1% mo, tr po + py	<0.2	17	230	<10	50
			27.92-28.00 m: barren qtz vein @ 70° to CA	17752				STANDARD					
			28.00-29.50 m: mo blebs + stringers @ 5° to CA	17753	25.00	26.50	1.50	2 x qtz-mo veins, tr mo	<0.2	13	138	<10	46
			29.50-31.00 m : 3 x mo stringers @ 30° to CA	17754	26.50	28.00	1.50	tr mo	0.2	14	65	<10	44
			32.50-34.59 m: mo stringers at 20° cut by qtz veins at 40° to CA with opposite dip angle; also qtz-mo veinlets at 60° to CA with same dip direction as the larger 40° vein set	17755	28.00	29.50	1.50	tr-1% mo	<0.2	9	284	<10	35
				17756	29.50	31.00	1.50	tr-0.5% mo	<0.2	13	36	<10	37
				17757	31.00	32.50	1.50	tr mo	0.4	44	95	<10	44
			34.59-36.06 m: QFP, more feldspar porphyry than qtz for 20 cm proximal to upper contact at ~20° to CA, rusty stained throughout; LC sharp @ 75° to CA	17758	32.50	34.59	2.09	tr-1% mo, tr py, po	<0.2	42	34	<10	47
				17759	34.59	36.06	1.47	tr-0.5% mo	<0.2	65	205	<10	41
				17760	36.06	37.50	1.44	tr mo	0.2	16	68	<10	43
			37.50-39.00 m: 6 qtz-mo stringers @ 30° to CA	17761	37.50	39.00	1.50	tr-0.5% mo	0.2	50	191	<10	41
			39.67-39.83 m: ser-chl? altn with veins and clots of mo	17762	39.00	39.83	0.83	tr-0.5% mo	0.2	87	270	<10	47
39.83	42.84		Biotite Alteration; intense and pervasive brown-black biotite? alteration with 15-25% porphyritic blebs of f-spar + qtz; UC gradational; LC sharp at 30° to CA	17763	39.83	41.33	1.50	tr mo	<0.2	47	94	<10	98
				17764	41.33	42.84	1.51	tr-0.5% mo	<0.2	20	195	<10	64
42.84	45.55		Quartz Porphyry; aphanitic; pale greenish-white; locally broken and fractured with rusty staining and manganese-oxides; multiple qtz-mo veinlets and one 6 mm wide massive py-cpy vein @ 65° to CA	17765	42.84	44.20	1.36	1% mo, 1% py, tr cpy	<0.2	42	82	<10	47
				17766	44.20	45.55	1.35	tr-0.5% mo, tr py	<0.2	47	118	<10	47

DIAMOND DRILL LOG

HOLE No. CM07-06

Interval		Rec'y %	Description	Sample No.	Interval		Core Width	Sample Description	Ag ppm	Cu ppm	Mo ppm	W ppm	Zn ppm
From	To				From	To							
45.55	49.40		Biotite Alteration; same as 39.83-42.84 m only locally well foliated at 70° to CA; irregular contacts	17767	45.55	47.47	1.92	tr mo	<0.2	17	186	<10	65
				17768	47.47	49.40	1.93	tr mo	<0.2	44	256	<10	70
49.40	50.64		Quartz Porphyry; as described 42.84-45.55 m, strong Fe-Ox staining at 50.22 m then transitional contact with underlying GD	17769	49.40	50.64	1.24	tr mo	<0.2	48	43	<10	62
50.64	81.05		Granodiorite; as described 11.68-39.83 m; locally broken and fractured as noted; mo as rare blebs, more commonly as qtz-mo veinlets + fx-fill 59.50-61.00 m: mo stringers at 5° to CA + mo blebs in qtz 61.00-62.50 m: minor cs-gr mo blebs 69.92-73.68 m: broken and fractured with pervasive rusty staining on fractures; local sections of more competent core; has dissm blebs of mo	17770	50.64	52.00	1.36	tr mo	<0.2	85	67	<10	42
				17771	52.00	53.50	1.50	tr mo	<0.2	18	57	<10	42
				17772	53.50	55.00	1.50	tr-1% mo, tr py + po	<0.2	32	475	<10	44
				17773				STANDARD					
				17774	55.00	56.50	1.50	tr mo	<0.2	30	0.066%	<10	46
				17775	56.50	58.00	1.50	tr-1% mo	<0.2	46	136	<10	52
				17776	58.00	59.50	1.50	tr mo	<0.2	67	184	<10	49
				17777	59.50	61.00	1.50	1-2% mo, tr py	<0.2	98	0.214%	<10	33
				17778	61.00	62.50	1.50	tr mo	<0.2	30	338	<10	46
				17779	62.50	64.00	1.50	tr mo	<0.2	43	250	<10	57
				17780	64.00	65.50	1.50	tr mo	<0.2	32	190	<10	45
				17781	65.50	67.00	1.50	tr mo	<0.2	11	19	<10	44
				17782	67.00	68.50	1.50	tr-0.5% mo	<0.2	22	202	<10	45
				17783	68.50	70.00	1.50	tr mo	<0.2	37	168	<10	41
17784	70.00	71.50	1.50	tr mo	<0.2	31	0.092%	<10	40				
17785	71.50	73.00	1.50	tr-0.5% mo	<0.2	83	0.163%	<10	26				
17786	73.00	74.50	1.50	tr-0.5% mo	<0.2	41	454	<10	37				

DIAMOND DRILL LOG

HOLE No. CM07-06

Interval		Rec'y %	Description	Sample No.	Interval		Core Width	Sample Description	Ag ppm	Cu ppm	Mo ppm	W ppm	Zn ppm
From	To				From	To							
			79.24-79.55 m: fault zone with white clay gouge, strongly calcareous	17787	74.50	76.00	1.50	tr-0.5% mo	<0.2	30	140	<10	33
				17788	76.00	77.50	1.50	tr mo	<0.2	24	54	<10	41
				17789	77.50	79.00	1.50	tr mo	<0.2	41	74	<10	90
				17790	79.00	81.05	2.05	tr-0.5% mo	<0.2	50	215	<10	46
81.05	105.95		Quartz Porphyry; aphanitic; pale greenish colour; 1-5% grey-translucent qtz eyes; prominent veinlets and fx-fill mo throughout unit, lightly fractured, locally moderately fractured with Fe-Ox 90.00-91.05 m: multiple mo veinlets at 70° to CA up to 3 mm, also in general for this unit are veins @ 50°, these are cut by set at 20° to CA + offset by up to 2 mm or the 50° set truncates at the 20° veins; also barren qtz veins at 20° to CA are offset by the 70° set 93.47-94.10 m: fractured with rusty staining	17791	81.05	82.50	1.45	tr mo	0.4	32	107	<10	33
				17792	82.50	84.00	1.50	tr-0.5% mo	1.2	388	31	<10	52
				17793	84.00	85.50	1.50	tr-1% mo	0.2	38	244	<10	31
				17794	85.50	87.00	1.50	1% mo	<0.2	59	0.138%	<10	53
				17795	87.00	88.50	1.50	tr-0.5% mo	<0.2	70	341	<10	42
				17796	88.50	90.00	1.50	tr-0.5% mo	0.2	53	261	<10	41
				17797				BLANK					
				17798	90.00	91.50	1.50	1-2% mo, tr py	0.2	103	0.152%	<10	26
				17799	91.50	93.00	1.50	1-2% mo	0.2	56	474	<10	46
				17800	93.00	94.50	1.50	1-2% mo	<0.2	58	201	<10	52
				17801	94.50	96.00	1.50	tr-1% mo	<0.2	40	433	<10	26
				17802	96.00	97.50	1.50	tr-1% mo	0.4	62	0.056%	<10	44
				17803	97.50	99.00	1.50	1-2% mo	<0.2	42	473	<10	23
			17804	99.00	100.50	1.50	1-2% mo	<0.2	65	0.055%	<10	24	
			17805	100.50	102.00	1.50	tr-0.5% mo	<0.2	49	112	<10	30	
			17806	102.00	103.50	1.50	tr-0.5% mo	<0.2	38	31	<10	35	
			17807	103.50	105.00	1.50	tr-0.5% mo	<0.2	48	81	<10	25	

DIAMOND DRILL LOG

HOLE No. CM07-06

Interval		Rec'y %	Description	Sample No.	Interval		Core Width	Sample Description	Ag ppm	Cu ppm	Mo ppm	W ppm	Zn ppm
From	To				From	To							
				17808	105.00	106.50	1.50	tr-0.5% mo	0.4	37	24	<10	32
105.95	123.53		Granodiorite; as previously described, massive and homogeneous; very minor mo as qtz-mo veins or fracture fill but density is only 1 veinlet / 2-3 m; UC sharp at 30° to CA with no alteration; LC sharp at 65° to CA with 4 mm wide band of qtz-bio at contact	17809	106.50	108.00	1.50	tr mo	<0.2	19	20	<10	45
				17810	108.00	109.00	1.00	tr-1% mo	1.2	989	0.087%	<10	112
				17811	109.00	110.00	1.00	tr mo	0.6	65	181	<10	38
				17812	122.53	123.53	1.00	nil mo	<0.2	53	29	<10	37
123.53	140.15		Quartz Porphyry; as described 81.05-105.95 m also with decent mo content but not as rich as the former interval; varies in colour from white to pale green over metre-scale sections; lightly fractured; LC sharp at 60° to CA	17813	123.53	125.00	1.47	tr mo	<0.2	40	126	<10	12
				17814	125.00	126.50	1.50	tr mo	0.4	60	344	<10	9
				17815	126.50	128.00	1.50	tr mo	<0.2	37	13	<10	12
				17816	128.00	129.50	1.50	tr-0.5% mo	<0.2	46	44	<10	16
				17817	129.50	131.00	1.50	tr mo, tr py	<0.2	52	98	<10	15
				17818				STANDARD					
				17819	131.00	132.50	1.50	tr-0.5% mo	<0.2	134	56	<10	191
				17820	132.50	134.00	1.50	tr mo	<0.2	38	37	<10	16
				17821	134.00	135.50	1.50	tr-0.5% mo	<0.2	48	0.052%	<10	15
				17822	135.50	137.00	1.50	tr-0.5% mo	<0.2	65	11	<10	106
17823	137.00	138.50	1.50	tr-1% mo	<0.2	110	38	<10	20				
17824	138.50	140.15	1.65	tr-0.5% mo	<0.2	54	39	<10	156				
140.15	146.57		Monzonite; massive equigranular, med-gr unit; not quite as mafic as the GD but could be a finer-grained version of the same unit; comprised mostly of qtz-fspar with 5% biotite locally altering to chlorite; has minor mo with qtz veins and as fx-fill; LC is fairly sharp at 65° to CA; mo veinlets mostly at 70° to CA	17825	140.15	141.50	1.35	tr mo	<0.2	75	38	<10	16
				17826	141.50	143.00	1.50	tr mo	<0.2	86	126	<10	12
				17827	143.00	144.50	1.50	tr-0.5% mo, tr py	<0.2	55	39	<10	19
				17828	144.50	145.50	1.00	tr mo	<0.2	59	134	<10	12

DIAMOND DRILL LOG

HOLE No. CM07-06

Interval		Rec'y %	Description	Sample No.	Interval		Core Width	Sample Description	Ag ppm	Cu ppm	Mo ppm	W ppm	Zn ppm
From	To				From	To							
				17829	145.50	146.57	1.07	tr mo	0.2	77	44	<10	17
146.57	155.37		Quartz Porphyry; as previously described; white to pale greenish colour; competent core, very lightly fractured; LC is a bit arbitrary	17830	146.57	148.00	1.43	tr mo, tr po + py	0.2	85	17	<10	22
				17831	148.00	149.50	1.50	tr mo	0.2	28	12	<10	23
				17832	149.50	151.00	1.50	tr-0.5% mo, tr py + po	0.2	49	28	<10	18
				17833	151.00	152.50	1.50	tr-0.5% mo	<0.2	50	76	<10	26
				17834	152.50	154.00	1.50	tr-0.5% mo	0.4	103	30	<10	15
				17835	154.00	155.37	1.37	tr-0.5% mo	<0.2	32	25	<10	44
155.37	173.03		Monzonite; about 80-90% monzonite with local intermixed GD and QP as dm-scale units; has 1-2% barren qtz veins 0.5-3.0 cm wide at 70° to CA; mo veins, when present, are mainly at 35° to CA and are a mo core with quartz; vein density is weak, 1-2/metre	17836	155.37	157.00	1.63	tr mo	<0.2	36	227	<10	40
				17837	157.00	158.50	1.50	1% mo, 2 main qtz-mo veins	<0.2	58	0.071%	<10	15
				17838	158.50	160.00	1.50	nil-tr mo	0.2	31	18	<10	47
				17839	160.00	161.50	1.50	nil-tr mo	<0.2	32	21	<10	45
				17840	161.50	163.00	1.50	tr mo	<0.2	53	80	<10	39
				17841	163.00	164.50	1.50	tr-0.5% mo, tr po + cpy	<0.2	88	10	<10	49
				17842	164.50	166.00	1.50	tr-0.5% mo	0.2	65	41	<10	40
				17843	166.00	167.50	1.50	tr mo, 2 x veinlets	0.2	85	15	<10	31
				17844	167.50	169.00	1.50	tr mo, 2 x veinlets	<0.2	66	33	<10	45
				17845	169.00	170.50	1.50	tr mo, 2 x veinlets	<0.2	30	23	<10	33
				17846	170.50	172.00	1.50	tr mo, 2 x veinlets	0.2	39	56	<10	42
				17847	172.00	173.03	1.03	tr-0.5% mo	0.2	62	59	<10	34

DIAMOND DRILL LOG

HOLE No. CM07-06

Interval		Rec'y %	Description	Sample No.	Interval		Core Width	Sample Description	Ag ppm	Cu ppm	Mo ppm	W ppm	Zn ppm		
From	To				From	To									
173.03	192.16		Heterolithic Breccia; comprised of fragments of granodiorite, qtz porphyry and minor monzonite with brown-black biotite alteration predominantly on the granodiorite; biotite also forms bands up to 30 cm wide, granodiorite is the most common fragment; upper contact is gradational and irregular; LC is also irregular; more sulphides, py and po, than in upper part of hole mostly as disseminated blebs or with qtz veining; mo veinlets at 45° + 65° to CA	17848	173.03	174.50	1.47	tr-0.5% mo	0.2	54	27	<10	94		
				17849	174.50	176.00	1.50	tr mo, tr py, 1% po	<0.2	145	9	<10	336		
				17850	176.00	177.50	1.50	tr mo, tr py, po, cpy	<0.2	168	9	<10	308		
				17851	177.50	179.00	1.50	tr each mo, po, cpy	0.2	78	4	<10	55		
				17852	179.00	180.50	1.50	tr-0.5% mo, tr po	<0.2	62	12	<10	46		
				17853	180.50	182.00	1.50	tr-0.5% mo, tr po	<0.2	52	73	<10	46		
				17854	182.00	183.50	1.50	tr-0.5% mo	<0.2	31	52	<10	69		
				17855				STANDARD							
				17856	183.50	185.00	1.50	tr-0.5% mo, 1% po	<0.2	129	24	<10	44		
				17857	185.00	186.50	1.50	tr mo, tr po	0.2	81	71	<10	45		
				17858	186.50	188.00	1.50	tr mo	<0.2	59	7	<10	56		
				17859	188.00	189.50	1.50	tr mo, tr po + py	<0.2	136	210	<10	58		
				17860	189.50	191.00	1.50	tr mo, tr po + py	0.4	89	6	<10	149		
				191.00-192.16 m: mo veinlets at 60-60° + 80° to CA	17861	191.00	192.16	1.16	tr-1% mo	0.4	126	83	<10	61	
192.16	198.23		Monzonite; as described 155.37-173.03 m; virtually no mineralization, sampled for continuity	17862	192.16	194.00	1.84	nil-tr mo	<0.2	57	17	<10	42		
				17863	194.00	196.00	2.00	nil-tr mo	0.4	80	32	<10	132		
				17864	196.00	198.23	2.23	nil-tr mo	0.4	78	42	<10	180		
			193.70-194.96 m: broken and fractured with rusty staining												
198.23	212.14		Quartz Porphyry / Monzonite; as previously described but also with feldspar and minor mafic minerals, could be a more felsic variation of the monzonite; decent mo veinlets throughout upper 2/3's of unit with veining at 45° + 65° to CA; 1-2 to 5-6 veins per metre	17865	198.23	200.00	1.77	tr-0.5% mo	<0.2	80	23	<10	529		
				17866	200.00	201.50	1.50	tr-1% mo, tr po + py	0.2	112	29	<10	611		
				17867	201.50	203.00	1.50	tr-1% mo, tr po + py	<0.2	117	34	<10	532		
				17868	203.00	204.50	1.50	tr mo, tr sulph	0.2	51	12	<10	171		

DIAMOND DRILL LOG

HOLE No. CM07-07

Property: Crack Moly	NTS:	Claim:	Elevation:	Azimuth: 180	Length: 297.18 m	Dip: -60
Coordinates: 585098 E / 5519402 N	Dip Tests:		Advance: 1693 m	Depth:	Date Collared: 09/09/07	Date Completed: 13/09/07
Purposes: IP Conductor	Drilled by: Westcore Drilling		Assays by: Eco Tech Labs		Logged by: Wesley Raven	

Interval		Rec'y %	Description	Sample No.	Interval		Core Width	Sample Description	Ag ppm	Cu ppm	Mo ppm	W ppm	Zn ppm
From	To				From	To							
0.00	1.82		Casing / Overburden										
1.82	14.33		Monzonite; medium grained; similar to granodiorite but with less mafics, 5-10%; and noticeably finer grained; rusty fractures throughout in oxide zone; has very minor qtz-mo veinlets at 40°; also qtz veins up to 1 cm at 20° to CA with cpy + py, veins are pitted and cut through mo stringers at 20° but with opposite dip; lower contact is transitional; limit of oxidation is 12.18 m; mo also present as disseminated flakes	17871A	1.82	3.50	1.68	tr mo	<0.2	43	166	<10	43
				17872A	3.50	5.00	1.50	nil-tr mo	0.2	81	32	<10	70
				17873A	5.00	6.50	1.50	nil-tr mo	0.4	56	44	<10	73
				17874	6.50	8.00	1.50	tr-1% mo, tr cpy, tr py	0.2	191	485	<10	77
				17875	8.00	9.50	1.50	tr mo, tr cpy, tr py, tr mal	0.4	97	0.052%	<10	78
				17876	9.50	11.00	1.50	tr mo, tr cpy, tr py, tr mal	0.2	26	198	<10	69
				17877	11.00	12.50	1.50	tr mo	0.4	31	268	<10	72
				17878	12.50	14.33	1.83	tr-0.5% mo	<0.2	53	236	<10	56
14.33	35.66		Granodiorite / Monolithic Breccia; difficult to ascertain if unit is a true breccia or just looks brecciated due to the pervasive biotite alteration; clasts are also GD enveloped by biotite; local aplite dykes as noted; minor qtz-mo veinlets + mo fx-fill and disseminations, overall sulphide content low	17879	14.33	16.00	1.67	tr mo, 1% py	0.2	144	141	<10	120
				17880	16.00	17.50	1.50	tr mo, tr py	0.2	93	59	<10	63
				17881	17.50	19.00	1.50	tr mo, tr cpy, py	<0.2	115	67	<10	62
				17882	19.00	20.50	1.50	tr-0.5% mo	<0.2	33	219	<10	65
				17883	20.50	22.00	1.50	tr mo	0.4	55	116	<10	65
				17884	22.00	23.50	1.50	tr mo	0.4	187	114	<10	63
				17885	23.50	25.00	1.50	tr mo	0.2	36	439	<10	59
				17886	25.00	26.50	1.50	tr mo	0.4	20	56	<10	56
17887	26.50	28.00	1.50	tr mo	0.2	41	68	<10	115				

DIAMOND DRILL LOG

HOLE No. CM07-07

Interval		Rec'y %	Description	Sample No.	Interval		Core Width	Sample Description	Ag ppm	Cu ppm	Mo ppm	W ppm	Zn ppm
From	To				From	To							
			63.73-65.80 m: mo stringers < 1 mm at 20°-30° to CA and from 65.34-65.72 m is rusty stained qtz vein at 20° to CA with tr sulph	17903	63.73	65.80	2.07	tr mo, tr sulph	<0.2	140	163	<10	49
69.68	103.49		Heterolithic Breccia; very similar to GD / monolithic brx but with addition of monzonite and QP clasts; no distinct contact, just the appearance of monzonite fragments 69.68-71.75 m: mo stringers at 35° to CA and dissemination and interstitial infilling around qtz fragments; at 70.20-70.38 m is broken with Fe-Ox staining around fx's @ 30° to CA 78.33-82.01 m: intermixed qtz porphyry and breccia, ~80% QP + 20% brx, contacts, when sharp, are at 80° to CA; network of narrow moly stringer veinlets throughout unit; veins at 35° + 55° to CA; at 79.26-79.38 m are 2 qtz veins with mo along margins, 1 cm vein at 30° to CA is cut by 2 cm vein at 30° to CA with opposite dip 92.77 m: 1 cm qtz-mo vein at 75° to CA 102.88-103.49 m: transitional contact from breccia to QP characterized by sausseritization of feldspars	17904	69.68	71.75	2.07	tr-0.5% mo	<0.2	46	470	<10	75
				17905	77.15	78.33	1.18	tr-0.5% mo	<0.2	63	442	<10	76
				17906	78.33	79.55	1.22	1% mo, tr cpy, py	0.2	250	0.055%	<10	103
				17907	79.55	80.77	1.22	tr-0.5% mo	<0.2	48	59	30	89
				17908	80.77	82.01	1.24	tr-0.5% mo	<0.2	29	141	<10	120
				17909				BLANK					
				17910	82.01	83.50	1.49	tr-0.5% mo, 1x1.5 cm qtz-mo vein @ 55° to CA	<0.2	52	304	<10	80
				17911	83.50	85.00	1.50	tr mo	<0.2	107	142	<10	65
				17912	85.00	86.52	1.52	nil-tr mo	<0.2	35	123	<10	65
103.49	114.00		Quartz Porphyry; aphanitic, pale green colour, lightly to moderately fractured with brownish-orange Fe-Ox staining as irregular saturations for up to several cm's around the fractures; lithological contacts are irregular; has up to 5% grey-translucent qtz eyes and 1-5% white feldspar										
114.00	137.36		Heterolithic to Monolithic Breccia; as described 69.68-103.49 m; very rare fragments of QP and virtually no monzonite; very little sulphide except over local intervals	17913	116.00	117.50	1.50	tr mo, cpy	0.2	222	355	<10	51
				17914	117.50	119.00	1.50	nil-tr sulph	0.4	88	5	<10	135
				17915	119.00	120.50	1.50	tr mo, po, cpy	0.2	97	441	<10	54

DIAMOND DRILL LOG

HOLE No. CM07-07

Interval		Rec'y %	Description	Sample No.	Interval		Core Width	Sample Description	Ag ppm	Cu ppm	Mo ppm	W ppm	Zn ppm
From	To				From	To							
			116.02 m: 2 cm qtz vein at 35° to CA with mo along margins + tr cpy blebs	17916	125.00	126.50	1.50	tr mo	<0.2	155	91	30	51
			119.09 m: 3 cm qtz vein at 25° to CA with cs-gr clots of mo-po-cpy	17917	126.50	128.00	1.50	tr mo	<0.2	108	100	20	58
				17918	128.00	129.50	1.50	tr mo, po, cpy	0.4	173	114	<10	53
			127.37-127.50 m: white qtz vein at 20° to CA; traces of mo in vein	17919	129.50	131.00	1.50	nil-tr sulph	<0.2	21	6	<10	68
				17920	131.00	132.50	1.50	nil-tr sulph	<0.2	55	40	<10	43
			132.54 m: 1 cm qtz-mo vein at 20° to CA	17921	132.50	134.00	1.50	nil-tr sulph	<0.2	18	2	<10	42
				17922	134.00	135.50	1.50	tr-0.5% mo	<0.2	37	21	<10	38
				17923	135.50	137.36	1.86	tr mo	<0.2	24	0.074%	<10	34
137.36	141.60		Quartz Porphyry; as previously described; pale greenish-white colour; solid competent core throughout with rusty staining on fx's at 35° to 45° to CA; has tr-2% py ± po as streaks (gash-like infill) and as "flowering" masses of euhedral py xals; very little mo in unit; UC sharp at 60° to CA; LC sharp at 45° to CA	17924	137.36	138.77	1.41	tr mo, 1-2% py ± po	<0.2	81	11	<10	21
				17925	138.77	140.18	1.41	tr mo, 1% py + po	<0.2	34	8	<10	12
				17926	140.18	141.60	1.42	tr mo, tr py	<0.2	47	4	<10	20
141.60	227.63		Heterolithic Breccia; as previously described	17927	141.60	143.00	1.40	nil-tr sulph	<0.2	46	165	<10	45
			146.00-147.50 m: mo-qtz veins at 50° and 30° to CA at 146.13-146.75 m shear zone with mo veinlets, Fe-Ox and QP, shear at ~50° to CA	17928	143.00	144.50	1.50	tr mo	<0.2	47	15	<10	41
				17929	144.50	146.00	1.50	tr mo	<0.2	80	2	10	46
				17930	146.00	147.50	1.50	0.5-1% mo, tr sulph	<0.2	82	406	<10	66
			162.09 m: shear zone with clay gouge; 1 cm wide at 50° to CA with carbonate	17931	147.50	149.00	1.50	tr mo	<0.2	60	27	<10	62
			165.62 m: 5 mm qtz-mo vein at 35° to CA	17932	168.08	169.50	1.42	tr-0.5% mo, tr sulph	<0.2	109	47	<10	66
			168.08-172.85 m: weak zone of qtz-mo veins, no obvious differences in this area vs. rest of unit except vein density	17933	169.50	171.00	1.50	tr mo, tr sulph	<0.2	69	3	<10	49
				17934	171.00	172.50	1.50	tr mo, po, py, cpy	0.2	85	104	<10	50

DIAMOND DRILL LOG

HOLE No. CM07-07

Interval		Rec'y %	Description	Sample No.	Interval		Core Width	Sample Description	Ag ppm	Cu ppm	Mo ppm	W ppm	Zn ppm
From	To				From	To							
			176.68-176.76 m: qtz vein @ 40° to CA with cs-gr clots of mo	17935	172.50	174.00	1.50	tr mo, po, py, cpy	<0.2	67	46	<10	51
				17936	174.00	175.50	1.50	tr mo, tr sulph	<0.2	34	13	10	121
			177.05-177.95 m: broken + fractured with sericite and broken qtz-mo veins	17937	175.50	177.00	1.50	tr-0.5% mo, tr py	<0.2	74	0.249%	<10	54
				17938	177.00	178.50	1.50	tr-0.5% mo	<0.2	64	172	<10	65
			177.05-184.33 m: pale green colour due to sericite + sausseritization	17939	178.50	180.00	1.50	tr mo	<0.2	34	10	<10	61
				17940	180.00	181.50	1.50	tr mo	<0.2	41	8	<10	42
				17941	181.50	183.00	1.50	tr mo	0.3	105	121	<10	46
			183.53-184.00 m: broken + fractured with clay gouge and qtz-mo veins + mo on fx's	17942	183.00	184.50	1.50	tr-0.5% mo	0.2	70	95	<10	58
				17943	184.50	186.00	1.50	tr-0.5% mo	0.2	132	75	<10	43
				17944	186.00	187.50	1.50	tr mo	0.2	49	21	<10	67
				17945	187.50	189.00	1.50	tr mo	<0.2	60	46	<10	79
			189.00-190.50 m: mo-qtz vein at 45° to CA	17946	189.00	190.50	1.50	tr-0.5% mo	<0.2	38	0.05%	<10	65
				17947	190.50	192.00	1.50	tr mo, tr sulph	<0.2	32	38	<10	66
			192.00-193.50 m: mo-qtz vein at 30° to CA, 6 mm wide	17948	192.00	193.50	1.50	tr mo, tr sulph	<0.2	78	94	<10	62
			193.50-195.00 m: 3 x mo-qtz veins 4-7 mm wide at 40° to CA	17949	193.50	195.00	1.50	0.5-1% mo, tr sulph	0.2	36	35	<10	50
				17950				STANDARD					
			195.00-196.50 m: 3 x mo-qtz veins with py + cpy at 30° + 45° to CA	17951	195.00	196.50	1.50	0.5% mo, tr py, cpy	<0.2	65	44	<10	82
			196.50-198.00 m: mo gash-infill in QP fragments	17952	196.50	198.00	1.50	tr mo	<0.2	137	54	<10	60
			203.50-204.23 m: silicified, clay + sausseritized	17953	203.50	205.00	1.50	tr mo, py, cpy	0.2	43	6	<10	78
			205.00-206.50 m: mo-qtz veins @ 25° to CA	17954	205.00	206.50	1.50	tr-0.5% mo, tr cpy	0.2	253	98	20	105

DIAMOND DRILL LOG

HOLE No. CM07-07

Interval		Rec'y %	Description	Sample No.	Interval		Core Width	Sample Description	Ag ppm	Cu ppm	Mo ppm	W ppm	Zn ppm
From	To				From	To							
			206.50-208.00 m: 3 x mo-py-qtz veins at 15°-30° to CA, qtz-mo vein at 50° to CA with opposite dip	17955	206.50	208.00	1.50	0.5% mo, tr cpy	0.6	322	198	<10	73
				17956	208.00	209.50	1.50	tr mo, tr cpy	0.6	273	15	<10	70
				17957	209.50	211.00	1.50	tr mo, tr cpy	0.2	136	73	<10	74
			213.05-213.30 m: broken + shattered with strong mo-qtz veins, shear @ 45° to CA	17958	211.00	212.50	1.50	tr mo, tr cpy	<0.2	86	36	<10	58
				17959	212.50	214.00	1.50	1-1.5% mo, tr py, cpy	0.3	202	0.089%	<10	59
			214.44-214.94 m: broken + fractured core with minor broken qtz-mo veins	17960	214.00	215.50	1.50	tr-0.5% mo, tr py, cpy	<0.2	60	102	<10	97
				17961	215.50	217.00	1.50	tr mo, tr sulph	0.4	161	27	<10	95
			217.00-218.50 m: py on fx's at 15° to CA	17962	217.00	218.50	1.50	tr-0.5% mo, tr py	0.2	111	39	<10	75
				17963	218.50	220.00	1.50	tr mo	<0.2	103	45	<10	71
227.63	229.42		Quartz Porphyry; greyish-white to pale green; contacts are irregular; has 1-2% narrow qtz veinlets 1-2 mm wide at 60° to CA with minor py; py also present on fx's										
229.42	243.80		Monolithic to Heterolithic Breccia; as previously described; breccia frags are mostly granodiorite with much rarer qtz porphyry	17964	236.50	238.00	1.50	tr mo	<0.2	84	17	<10	74
				17965	238.00	239.22	1.22	tr cpy	<0.2	47	3	<10	76
			229.99-230.65 m: qtz porphyry with one mo vein ~ 1-2 mm wide at ~40 to CA; UC sharp at 60° to CA, LC sharp at 15° to CA	17966	239.22	240.09	0.87	tr mo, py	<0.2	27	3	<10	46
				17967	240.09	241.94	1.85	nil sulph	<0.2	62	3	<10	58
			239.22-240.09 m: QP, irregular contacts	17968	241.94	243.80	1.86	tr mo, tr py	<0.2	63	3	<10	67
243.80	249.21		Quartz Porphyry / Aplite Dyke; not typical of QP, fine-grained, pale green colour, looks like flow-banded rhyolite; moderately to strongly broken + fractured throughout; has 1-2% narrow, grey qtz veinlets at 50-55° to CA ± sulphides; contacts are irregular	17969	243.80	245.30	1.50	tr mo, py	0.2	45	3	<10	55
				17970	245.30	246.80	1.50	tr mo, py	<0.2	56	4	<10	94
				17971	246.80	248.30	1.50	tr mo, py	<0.2	27	4	<10	79
				17972	248.30	249.21	0.91	tr mo, py	<0.2	41	9	<10	62

DIAMOND DRILL LOG

HOLE No. CM07-07

Interval		Rec'y %	Description	Sample No.	Interval		Core Width	Sample Description	Ag ppm	Cu ppm	Mo ppm	W ppm	Zn ppm	
From	To				From	To								
249.21	259.45		Heterolithic Breccia; as previously described 249.21-250.50 m: 1 x qtz-mo vein, 3 mm wide at 15° to CA 252.28-259.45 m: a mix of breccia (80%) and qtz porphyry (20%) with zones of green alteration (sericite) around qtz veins and local shear zones with clay; qtz veins have minor sulphides, are several cm's wide, and at 25° and 50° to CA	17973	249.21	250.50	1.29	tr mo, tr sulph	<0.2	28	<1	<10	62	
				17974	250.50	252.00	1.50	tr mo, tr sulph	<0.2	31	20	<10	70	
				17975				BLANK						
				17976	252.00	253.50	1.50	tr mo, tr sulph	0.3	40	4	<10	74	
				17977	253.50	255.00	1.50	tr-0.5% mo, tr sulph	<0.2	90	21	<10	96	
				17978	255.00	256.50	1.50	tr mo, tr sulph	<0.2	58	2	20	78	
				17979	256.50	258.00	1.50	tr mo, tr sulph	<0.2	40	10	<10	94	
				17980	258.00	259.45	1.45	tr mo, tr sulph	0.2	109	5	<10	61	
259.45	261.96		Quartz Porphyry; as previously described, moderately to locally strongly broken + fractured; qtz-mo-py ± cpy veinlets at 30°-35° to CA, contacts are irregular	17981	259.45	260.70	1.25	tr mo, tr sulph	<0.2	147	12	<10	94	
				17982	260.70	261.96	1.26	tr mo, tr sulph	0.2	83	13	<10	182	
261.96	286.08		Heterolithic Breccia; as previously described 274.50-279.50 m: weak qtz-mo-sulp veins and green coloured zones of sausseritization; veins/fractures at 10-15° to CA	17983	261.96	263.50	1.54	tr mo, tr sulph	0.4	49	4	<10	87	
				17984	263.50	265.00	1.50	tr-0.5% mo, tr sulph	0.4	53	2	10	144	
				17985	265.00	266.50	1.50	tr mo, tr sulph	<0.2	28	3	<10	58	
				17986	266.50	268.00	1.50	tr-0.5% mo, tr sulph	<0.2	65	4	<10	71	
				17987	274.50	276.00	1.50	tr-0.5% mo, tr sulph	<0.2	72	134	<10	58	
				17988	276.00	277.50	1.50	tr mo, py, po, cpy	<0.2	105	3	<10	50	
				17989	277.50	278.50	1.00	tr mo, py, po, cpy	0.4	22	<1	<10	49	
				17990	278.50	279.50	1.00	tr mo, py, po, cpy	<0.2	46	16	<10	56	
286.08	290.56		Quartz Porphyry; as previously described; moderately broken and fractured; mo veinlets and gash infill; UC fairly sharp at 40° to CA; LC is drawn out along a quartz vein at ~10-15° to CA	17991	286.08	287.58	1.50	tr-0.5% mo, tr-1% py	<0.2	60	16	<10	89	
				17992	287.58	289.08	1.50	tr-0.5% mo, tr-1% py	<0.2	42	25	<10	116	

DIAMOND DRILL LOG

HOLE No. CM07-08

Property: Crack Moly	NTS:	Claim:	Elevation: 1768 m	Azimuth: 000	Length: 331.93 m	Dip: -76°
Coordinates: 584745 E / 5519236 N	Dip Tests:		Advance:	Depth:	Date Collared: 14/09/07	Date Completed: 18/09/07
Purposes: IP Anomaly	Drilled by: Westcore Drilling		Assays by: Eco Tech		Logged by: Mike Miller	

Interval		Rec'y %	Description	Sample No.	Interval		Core Width	Sample Description	Ag ppm	Cu ppm	Mo ppm	W ppm	Zn ppm
From	To				From	To							
0.00	1.48		Casing / Overburden										
1.48	331.93		Granodiorite; Fe-oxide stained, weathered, biotite porphyritic	18001	4.12	5.18	1.06		1.4	53	50	<10	58
				18002	5.18	6.85	1.67		0.6	47	19	<10	66
			6.62-22.16 m: no partings, qtz veins at 20° to CA, wk bio alteration along 1 cm bands parallel to CA	18003	8.23	9.75	1.52		1	32	20	<10	122
				18004	9.75	11.28	1.53		1.1	97	56	<10	342
				18005	11.28	12.70	1.42		0.6	24	16	<10	121
				18006	12.70	14.16	1.46		<0.2	16	120	<10	55
				18007	14.16	15.54	1.38		0.6	13	252	<10	76
				18008	15.54	16.98	1.44		2	16	33	<10	92
				18009	16.98	18.42	1.44		3	31	77	<10	83
				18010	18.42	19.99	1.57		8.6	66	21	<10	169
				18011	19.99	21.49	1.50		0.2	21	11	<10	78
				18012	24.00	25.75	1.75		0.7	60	58	<10	202
			27.14-38.71 m: unaltered to weakly foliated, from 31.85-32.61 m: very broken and unoxidized	18013	25.75	27.18	1.43		0.8	83	0.050%	<10	267
				18014				STANDARD					
			38.17-40.33 m: very weathered with iron oxide staining, sericitic fault gouge; sausseritized	18015	32.61	33.95	1.34		1.4	16	27	<10	100
				18016	33.95	35.66	1.71		2.4	40	51	<10	258
				18017	35.66	37.28	1.62		3.6	41	65	<10	161

DIAMOND DRILL LOG

HOLE No. CM07-08

Interval		Rec'y %	Description	Sample No.	Interval		Core Width	Sample Description	Ag ppm	Cu ppm	Mo ppm	W ppm	Zn ppm
From	To				From	To							
			40.33-47.37 m: massive to foliated, some oxidation	18018	37.28	38.77	1.43		0.8	18	23	<10	92
			47.37-53.25 m: iron oxide staining	18019	61.84	63.24	1.40		3	15	69	<10	67
				18020	63.24	64.67	1.43		<0.2	32	85	<10	62
				18021	64.67	66.67	1.70		2.4	62	119	<10	96
				18022	72.27	74.15	1.91		1.7	156	76	<10	348
				18023	74.15	76.21	2.06		3.4	780	113	<10	116
				18024	76.21	77.73	1.52		0.8	258	75	<10	59
				18025	77.73	79.29	1.56		1.6	31	68	<10	61
				18026	79.29	80.64	1.35		0.2	51	17	<10	52
				18027	80.64	82.28	1.64		<0.2	64	23	<10	109
				18028	88.66	90.16	1.50		0.4	53	38	<10	66
				18029	90.16	91.56	1.40		4.2	27	8	<10	92
				18030	91.56	93.49	1.93		1.4	567	33	<10	93
				18031	93.49	94.90	1.41		3.2	44	44	<10	82
				18032	94.90	96.36	1.46		2	53	30	<10	66
				18033	97.16	98.66	1.50		3.4	82	48	<10	103
				18034	104.14	105.85	1.71		0.2	18	114	<10	63
				18035	105.85	107.33	1.48		0.6	19	60	<10	104
				18036	107.33	108.94	1.61		<0.2	54	137	<10	108
				18037	110.43	111.86	1.43		1.1	49	0.106%	<10	129
				18038	111.86	113.36	1.50		1.2	166	35	<10	377

DIAMOND DRILL LOG

HOLE No. CM07-08

Interval		Rec'y %	Description	Sample No.	Interval		Core Width	Sample Description	Ag ppm	Cu ppm	Mo ppm	W ppm	Zn ppm	
From	To				From	To								
				18039	113.36	114.83	1.47	STANDARD	0.6	216	45	<10	128	
				18040	114.83	116.28	1.45		<0.2	41	19	<10	174	
				18041										
				18042	116.28	117.79	1.51		1.3	23	30	<10	87	
				18043	119.22	120.79	1.57		<0.2	121	89	<10	73	
				18044	120.79	122.23	1.44		<0.2	110	234	<10	206	
				18045	122.23	123.70	1.47		<0.2	63	18	<10	65	
				18046	123.70	125.20	1.50		<0.2	133	50	<10	107	
				18047	126.56	128.09	1.53		0.2	154	32	<10	54	
				18048	128.09	129.59	1.50		<0.2	74	15	<10	123	
				18049	129.59	131.09	1.50		<0.2	143	68	<10	127	
				18050	131.59	133.09	1.50		<0.2	69	31	<10	132	
				18051	133.09	135.43	2.34		0.5	279	42	<10	144	
				18052	135.43	137.14	1.71		<0.2	52	470	<10	66	
				18053	137.14	138.71	1.57		1.1	112	44	<10	102	
				18054					BLANK					
				18055	138.71	140.20	1.49			<0.2	102	65	<10	102
				18056	140.20	141.67	1.47	1.4		940	177	<10	502	
				18057	141.67	143.17	1.50	<0.2		54	94	<10	92	
				18058	145.51	147.03	1.52	<0.2		81	67	<10	78	
				18059	147.03	148.52	1.49	0.2		175	71	<10	253	

DIAMOND DRILL LOG

HOLE No. CM07-08

Interval		Rec'y %	Description	Sample No.	Interval		Core Width	Sample Description	Ag ppm	Cu ppm	Mo ppm	W ppm	Zn ppm
From	To				From	To							
				18060	148.52	149.98	1.46		<0.2	13	37	<10	61
				18061	149.98	151.49	1.51		0.2	30	44	<10	61
				18062	151.49	153.00	1.51		10.4	22	14	<10	101
				18063	153.00	154.53	1.53		0.6	300	80	<10	65
				18064	154.53	156.01	1.48		<0.2	41	66	<10	70
				18065	156.01	157.58	1.57		0.4	31	76	<10	75
				18066	161.50	163.05	1.55		0.6	27	34	<10	126
				18067	164.48	166.00	1.52		0.4	211	52	<10	75
				18068	166.00	167.50	1.50		<0.2	7	47	<10	81
				18069	167.50	168.96	1.46		0.4	22	59	<10	103
				18070	170.15	171.67	1.52		<0.2	34	39	<10	69
				18071	171.67	173.30	1.63		0.2	107	21	<10	65
				18072				STANDARD					
				18073	173.30	174.81	1.51		0.2	36	54	<10	93
				18074	176.41	177.83	1.42		0.2	20	88	<10	54
				18075	177.83	179.62	1.79		<0.2	24	148	<10	62
				18076	180.78	182.50	1.72		<0.2	33	25	<10	68
				18077	183.50	185.01	1.51		<0.2	86	28	<10	152
				18078	185.01	186.75	1.74		0.6	254	31	<10	95
				18079	186.75	188.13	1.38		<0.2	26	68	<10	77
				18080	188.13	189.63	1.50		<0.2	99	45	<10	274

DIAMOND DRILL LOG

HOLE No. CM07-08

Interval		Rec'y %	Description	Sample No.	Interval		Core Width	Sample Description	Ag ppm	Cu ppm	Mo ppm	W ppm	Zn ppm
From	To				From	To							
				18081	189.63	191.11	1.48		<0.2	10	64	<10	59
				18082				STANDARD					
				18083	192.53	194.03	1.50		<0.2	10	35	<10	68
				18084	196.20	197.48	1.28		<0.2	7	37	<10	52
				18085	200.25	201.55	1.30		0.2	108	212	<10	32
				18086	207.25	208.75	1.50		<0.2	29	69	<10	65
				18087	208.75	210.22	1.47		<0.2	22	18	<10	76
				18088	210.22	211.75	1.53		0.6	71	46	<10	107
				18089	211.75	214.14	2.39		<0.2	120	34	<10	71
				18090	215.99	217.45	1.46		<0.2	52	118	<10	67
				18091	217.45	218.91	1.46		<0.2	17	22	<10	66
				18092	218.91	219.42	0.51		0.4	148	100	<10	52
				18093	219.42	221.88	2.46		<0.2	124	36	<10	108
				18094	221.88	223.38	1.50		0.2	192	34	<10	167
				18095	224.89	226.42	1.53		0.2	376	60	<10	99
				18096	227.69	229.20	1.51		0.2	85	72	<10	180
				18097	229.20	230.70	1.50		0.5	78	53	<10	159
				18098	234.64	236.14	1.50		1.6	994	44	<10	271
				18099	237.43	238.87	1.44		0.4	161	36	<10	87
				18100	238.87	240.40	1.53		<0.2	102	253	<10	102
				18101	240.40	242.08	1.68		0.4	360	55	<10	126

DIAMOND DRILL LOG

HOLE No. CM07-08

Interval		Rec'y %	Description	Sample No.	Interval		Core Width	Sample Description	Ag ppm	Cu ppm	Mo ppm	W ppm	Zn ppm
From	To				From	To							
				18102	242.93	244.50	2.42		0.4	195	135	<10	132
				18103	244.50	245.97	1.47		<0.2	61	52	<10	231
				18104	245.97	247.66	1.69		<0.2	18	146	<10	49
				18105	247.66	249.02	1.36		<0.2	22	42	<10	56
				18106	249.02	250.65	1.63		<0.2	10	47	<10	49
				18107	250.65	252.07	1.42		<0.2	22	85	<10	52
				18108	252.07	253.97	1.90		<0.2	19	35	<10	51
				18109	255.12	256.63	1.51		<0.2	20	49	<10	64
				18110	256.63	258.17	1.54		<0.2	43	17	<10	55
				18111	258.17	259.79	1.62		<0.2	26	211	<10	53
				18112	259.79	261.47	1.68		<0.2	20	37	<10	53
				18113	261.47	262.89	1.42		0.4	188	8	<10	387
				18114	264.83	266.44	1.61		<0.2	28	322	<10	52
				18115	266.44	267.94	1.50		0.2	75	21	<10	49
				18116	267.94	269.44	1.50		<0.2	22	15	<10	56
				18117	270.35	271.85	1.50		<0.2	36	46	<10	87
				18118	271.85	273.38	1.53		<0.2	12	55	<10	52
				18119	273.38	274.64	1.26		<0.2	47	198	<10	53
				18120	276.01	277.50	1.49		0.2	59	53	<10	82
				18121	277.50	278.98	1.48		<0.2	38	60	<10	55
				18122	280.86	282.34	1.48		<0.2	96	167	<10	60

DIAMOND DRILL LOG

HOLE No. CM07-08

Interval		Rec'y %	Description	Sample No.	Interval		Core Width	Sample Description	Ag ppm	Cu ppm	Mo ppm	W ppm	Zn ppm
From	To				From	To							
				18123	282.34	283.85	1.51		<0.2	41	26	<10	129
				18124	283.85	285.36	1.51		<0.2	31	140	<10	54
				18125	285.36	286.71	1.35		<0.2	47	73	<10	56
				18126	286.71	288.40	1.69		<0.2	41	23	<10	63
				18127	288.40	289.80	1.40		<0.2	79	78	<10	67
				18128	292.22	293.63	1.41		<0.2	71	57	<10	52
				18129	298.48	300.09	1.61		<0.2	47	30	<10	50
				18130	300.09	301.60	1.51		<0.2	76	168	<10	47
				18131	301.60	303.08	1.48		<0.2	45	198	<10	51
				18132	303.08	304.60	1.52		<0.2	41	0.050%	<10	64
				18133	304.60	306.42	1.82		<0.2	30	102	<10	54
				18134	311.15	312.52	1.37		<0.2	40	33	<10	47
				18135	312.52	313.99	1.47		<0.2	93	49	<10	47
				18136	313.99	315.35	1.36		<0.2	331	45	<10	46
				18137	318.19	319.67	1.48		<0.2	56	8	<10	42
				18138	326.90	328.73	1.83		<0.2	146	102	<10	44
				18139	328.73	329.18	0.45		<0.2	146	0.067	<10	49
				18140	329.18	331.78	2.60		<0.2	144	44	<10	25

DIAMOND DRILL LOG

HOLE No. CM07-09

Interval		Rec'y %	Description	Sample No.	Interval		Core Width	Sample Description	Ag ppm	Cu ppm	Mo ppm	W ppm	Zn ppm	
From	To				From	To								
74.88	90.53		Granodiorite; fractured and oxidized sections; at 76.30-76.90 m is pegmatite with intergrown qtz-feldspar; epidote alteration in 20 cm sections common; from 80.60-81.03 m is very oxidized and crumbly	18184	75.29	76.60	1.31		<0.2	109	89	<10	47	
				18185	76.60	78.08	1.48		<0.2	96	114	<10	51	
				18186	80.30	81.80	1.50		<0.2	75	176	20	95	
				18187	86.69	88.34	1.65		<0.2	73	79	<10	59	
90.53	95.78		Quartz Porphyry; unoxidized; occasional mo partings; UC sharp at 50° to CA, LC sharp @ 45° to CA	18188	90.53	92.23	1.70		<0.2	120	241	<10	30	
95.78	100.49		Granodiorite; non-mineralized											
100.49	109.88		Quartz Porphyry; as previously described, competent; tr mo in partings, qtz veins near bottom of unit	18189	108.15	109.68	1.53		0.7	235	118	<10	66	
109.88	123.81		Granodiorite; very fine grained mo in qtz veins 120.84-121.30 m: Q.P., minor mo	18190	109.68	111.50	1.82	STANDARD	<0.2	72	124	<10	57	
				18191										
				18192	111.86	113.38	1.52		<0.2	67	255	<10	64	
				18193	113.38	114.91	1.53		<0.2	15	0.087%	<10	45	
				18194	114.91	116.18	1.27		<0.2	47	430	<10	49	
				18195	116.18	117.80	1.62		<0.2	38	0.049%	<10	50	
				18196	117.80	119.30	1.50		<0.2	57	191	<10	156	
				18197	119.30	120.84	1.54		<0.2	36	148	<10	77	
				18198	120.84	121.30	0.46		0.2	77	289	<10	76	
				18199	121.30	122.70	1.40		<0.2	135	106	<10	54	
18200	122.70	123.40	0.70	<0.2	23	66	20	65						
123.81	126.21		Quartz Porphyry; as previously described	18201	123.40	126.21	2.81		0.2	86	425	<10	144	

DIAMOND DRILL LOG

HOLE No. CM07-09

Interval		Rec'y %	Description	Sample No.	Interval		Core Width	Sample Description	Ag ppm	Cu ppm	Mo ppm	W ppm	Zn ppm
From	To				From	To							
126.21	198.87		Granodiorite; fine-grained becoming coarser-grained downhole; locally broken and crumbly with fe-ox staining; core washed away at 158.00-160.00 m; LC with carbonate and cut by mo partings	18202	126.21	127.85	1.64		0.2	193	93	20	97
				18203	127.85	129.18	1.33		<0.2	64	492	<10	59
				18204	129.18	130.90	1.72		0.7	265	123	<10	84
				18205	131.45	132.95	1.50		0.2	186	340	<10	43
				18206	132.95	134.45	1.50		0.4	171	112	<10	49
				18207	137.17	138.67	1.50		0.2	57	157	<10	52
				18208	138.67	140.17	1.50		0.4	153	52	<10	99
				18209	145.97	147.59	1.62		<0.2	55	50	<10	57
				18210	149.57	151.07	1.50		0.8	391	32	<10	74
				18211	154.53	155.91	1.38		<0.2	41	113	<10	56
				18212	155.91	157.51	1.60		0.4	216	107	<10	68
				18213	157.51	159.01	1.50		0.2	50	173	<10	50
				18214	163.68	165.18	1.50		0.4	224	43	<10	54
				18215	165.18	166.72	1.54		0.8	436	132	<10	52
				18216	166.72	168.12	1.40		<0.2	204	434	<10	45
				18217	168.12	169.77	1.65		0.4	323	180	<10	43
				18218	169.77	171.32	1.55		0.4	224	39	<10	62
				18219	171.32	172.82	1.50		0.8	317	202	<10	51
				18220	172.82	174.17	1.35		1.3	1024	101	<10	190
				18221	174.17	175.87	1.70		0.5	220	169	<10	52
				18222	175.87	177.50	1.63		0.3	109	46	<10	53


DIAMOND DRILL LOG

HOLE No. CM07-09

Interval		Rec'y %	Description	Sample No.	Interval		Core Width	Sample Description	Ag ppm	Cu ppm	Mo ppm	W ppm	Zn ppm
From	To				From	To							
				18223	177.50	179.01	1.51		0.2	213	78	30	224
				18224	179.01	180.58	1.57		0.4	174	172	<10	65
				18225	180.58	182.02	1.44		0.3	40	192	<10	53
				18226	182.02	183.55	1.53		0.4	236	71	<10	82
				18227	183.55	185.01	1.46		0.6	209	121	<10	52
				18228	185.01	186.51	1.50		0.4	122	172	<10	53
				18229	186.51	188.06	1.55		0.7	333	60	<10	53
				18230	188.06	189.67	1.61		0.2	29	90	<10	70
				18231	189.67	191.11	1.44		0.4	74	53	<10	90
				18232	191.11	192.71	1.60		0.4	83	56	<10	115
				18233	192.71	194.16	1.45		0.2	47	80	<10	62
				18234	194.16	195.72	1.56		<0.2	28	126	<10	58
				18235	195.72	197.21	1.49		2.4	1345	307	<10	127
				18236	197.21	198.87	1.66		0.2	92	463	<10	68
198.87	238.05		Quartz Porphyry; as previously described	18237	198.87	200.25	1.38		0.2	84	238	<10	151
				18238	200.25	201.75	1.50		0.2	49	180	<10	118
				18239	201.75	203.30	1.55		0.4	119	354	<10	121
				18240	203.30	204.82	1.52		0.2	71	317	<10	142
				18241	204.82	206.31	1.49		0.2	68	237	<10	160
				18242	212.31	213.80	1.49		<0.2	121	162	<10	124
				18243	221.59	223.09	1.50		<0.2	166	88	<10	247

Appendix 2.

Assay Results

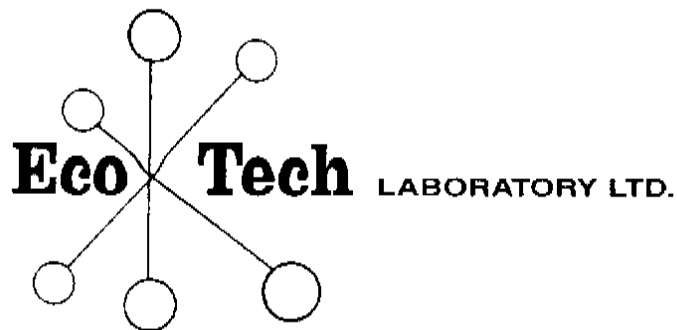

ASSAYING, GEOCHEMISTRY
ANALYTICAL CHEMISTRY
ENVIRONMENTAL TESTING
ISO 9001 Accredited Co.

10041 Dallas Drive, Kamloops, BC V2C 6T4
Phone (250) 573-5700 Fax (250) 573-4557
E-mail: info@ecotechlab.com
www.ecotechlab.com

CERTIFICATE OF ASSAY AK 2007-1624

Pacific Cascade Resources
520 - 700 W. Pender Street
Vancouver, BC
V6C 1G8

26-Nov-07

No. of samples received: 132
Sample Type: Core
Project: Crack Moly
Submitted by: Wesley Raven

ET #.	Tag #	Mo (%)
16	7R18165	0.063
42	7R18191	0.065
44	7R18193	0.087
46	7R18195	0.049

QC DATA:


Repeat:

44	7R18193	0.085
----	---------	-------

Standards:

MP2	0.280
MP2	0.284

JJ/nl
XLS/07

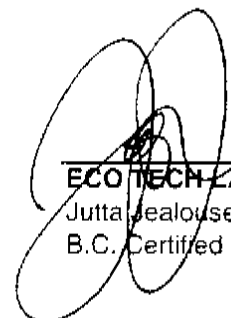

ECO TECH LABORATORY LTD.
Jutta Jealouse
B.C. Certified Assayer

ECO TECH LABORATORY LTD.

10041 Dallas Drive

KAMLOOPS, B.C.

V2C 6T4

ICP CERTIFICATE OF ANALYSIS AK 2007- 1624

Pacific Cascade Resources

520 - 700 W. Pender Street

Vancouver, BC

V6C 1G8

Phone: 250-573-5700

Fax : 250-573-4557

No. of samples received: 94

Sample Type: Core

Project: Crack Moly

Submitted by: Mike

Values in ppm unless otherwise reported

Et #.	Tag #	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	K%	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
1	7R18150	0.4	6.51	15	620	285	2.63	<1	2	94	225	1.58	0.88	<10	0.43	292	111	2.47	6	590	30	<5	<20	692	0.22	<10	35	10	2	73
2	7R18151	<0.2	6.69	15	630	10	2.04	<1	2	107	138	1.84	1.09	<10	0.45	295	213	2.57	7	620	30	<5	<20	697	0.24	<10	39	<10	2	69
3	7R18152	<0.2	6.23	10	620	25	2.86	<1	2	84	43	1.43	0.75	<10	0.40	286	101	2.62	5	570	24	<5	<20	692	0.23	<10	32	<10	2	52
4	7R18153	<0.2	6.53	10	650	<5	2.91	<1	2	103	20	1.50	0.76	<10	0.44	275	41	2.73	5	560	26	<5	<20	735	0.24	<10	33	<10	3	62
5	7R18154	0.2	6.59	10	610	70	2.41	<1	2	85	83	1.61	1.07	<10	0.41	306	278	2.45	6	560	28	<5	<20	671	0.22	<10	35	20	2	65
6	7R18155	<0.2	6.38	10	595	<5	2.85	<1	2	102	26	1.47	0.79	<10	0.40	273	59	2.68	6	560	26	<5	<20	700	0.23	<10	34	<10	3	58
7	7R18156	<0.2	7.20	10	645	<5	2.87	<1	2	84	36	1.52	0.77	<10	0.44	273	248	2.60	6	580	32	<5	<20	753	0.23	<10	33	<10	3	65
8	7R18157	<0.2	6.55	10	595	<5	2.86	<1	2	87	42	1.47	0.74	<10	0.41	282	22	2.75	6	550	24	<5	<20	714	0.23	<10	32	<10	2	60
9	7R18158	<0.2	6.15	10	540	<5	2.51	<1	1	69	97	1.43	0.98	<10	0.40	309	124	2.57	5	520	26	<5	<20	640	0.20	<10	31	20	2	60
10	7R18159	<0.2	6.42	10	510	<5	2.53	<1	2	73	40	1.42	0.86	<10	0.41	282	21	2.59	5	510	28	<5	<20	683	0.22	<10	31	20	3	70
11	7R18160	0.2	6.29	10	615	15	2.50	<1	2	124	77	1.51	0.86	<10	0.39	289	114	2.44	6	520	26	<5	<20	659	0.20	<10	32	<10	2	52
12	7R18161	<0.2	6.55	10	645	<5	2.77	<1	2	95	39	1.47	0.77	<10	0.42	283	120	2.69	5	530	28	<5	<20	707	0.22	<10	31	<10	2	76
13	7R18162	<0.2	6.66	10	620	<5	2.81	<1	2	92	46	1.51	0.80	<10	0.43	256	46	2.66	5	560	26	<5	<20	705	0.23	<10	35	<10	3	53
14	7R18163	<0.2	6.50	10	625	<5	2.50	<1	2	116	77	1.51	0.85	<10	0.42	294	31	2.57	6	540	28	<5	<20	700	0.22	<10	34	<10	2	59
15	7R18164	<0.2	6.41	10	610	<5	2.54	<1	2	86	43	1.47	0.86	<10	0.41	296	124	2.39	5	550	24	<5	<20	644	0.23	<10	34	70	2	66
16	7R18165	<0.2	7.19	15	1005	<5	2.06	<1	6	22	121	2.77	3.02	30	0.66	705	654	1.39	18	1030	20	<5	<20	411	0.30	<10	50	<10	18	91
17	7R18166	<0.2	7.05	15	615	<5	2.64	<1	1	91	11	1.44	0.78	<10	0.38	335	8	2.96	5	550	28	<5	<20	722	0.22	<10	27	<10	2	61
18	7R18167	<0.2	6.71	10	615	<5	2.65	<1	2	84	27	1.46	0.76	<10	0.42	325	93	2.68	5	550	28	<5	<20	695	0.22	<10	33	<10	2	57
19	7R18168	0.4	6.32	10	610	<5	2.63	<1	2	78	32	1.41	0.76	<10	0.41	298	61	2.71	4	520	26	<5	<20	668	0.22	<10	32	20	2	58
20	7R18169	<0.2	6.58	50	1040	40	2.35	<1	2	76	170	1.53	1.21	<10	0.34	323	75	2.30	5	530	28	<5	<20	566	0.20	<10	35	<10	2	58
21	7R18170	<0.2	6.58	10	560	<5	2.73	<1	2	82	31	1.58	0.80	<10	0.41	287	11	2.79	6	560	26	<5	<20	666	0.23	<10	35	<10	2	56
22	7R18171	0.2	6.12	10	1525	80	0.83	<1	<1	63	92	0.71	2.97	10	0.06	92	81	1.63	2	150	40	<5	<20	274	0.02	<10	3	<10	13	73
23	7R18172	<0.2	6.52	10	525	<5	2.41	<1	2	91	49	1.71	1.02	<10	0.38	319	99	2.61	5	550	26	<5	<20	611	0.23	<10	33	<10	2	57
24	7R18173	<0.2	7.05	15	600	<5	2.86	<1	2	98	31	1.63	0.85	<10	0.43	293	98	2.83	6	570	26	<5	<20	691	0.24	<10	34	10	3	57
25	7R18174	<0.2	6.79	10	595	<5	2.47	<1	2	82	46	1.63	0.87	<10	0.41	301	26	2.57	5	580	26	<5	<20	656	0.24	<10	33	<10	2	55

Et #.	Tag #	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	K%	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
26	7R18175	<0.2	6.18	15	390	<5	0.51	2	<1	57	92	0.68	3.32	<10	0.05	124	91	1.93	2	210	32	<5	<20	155	0.01	<10	2	<10	15	109
27	7R18176	0.2	5.59	15	205	70	0.31	2	<1	62	75	0.71	2.85	<10	0.04	315	217	1.81	2	190	34	<5	<20	99	0.01	<10	3	<10	15	122
28	7R18177	<0.2	7.32	10	180	35	0.46	1	<1	55	56	0.81	2.97	<10	0.04	484	89	2.17	3	240	42	<5	<20	85	0.01	<10	1	<10	16	105
29	7R18178	0.2	6.96	30	225	20	0.43	3	<1	52	67	0.70	3.25	<10	0.04	285	86	1.99	2	220	38	<5	<20	121	0.01	<10	2	<10	15	153
30	7R18179	0.2	6.50	25	390	15	0.27	2	<1	56	98	0.68	3.49	<10	0.04	70	66	1.53	2	190	32	<5	<20	140	<0.01	<10	2	<10	14	185
31	7R18180	<0.2	6.20	40	290	15	0.29	1	<1	62	73	0.64	3.18	<10	0.03	61	77	1.89	2	200	34	<5	<20	113	<0.01	<10	4	<10	14	78
32	7R18181	<0.2	6.95	20	365	20	0.46	2	<1	58	103	0.72	3.48	10	0.04	257	182	1.73	2	200	36	<5	<20	183	<0.01	<10	4	10	19	161
33	7R18182	<0.2	6.59	15	495	<5	2.23	2	2	83	103	1.49	1.19	<10	0.34	291	49	2.53	5	540	24	<5	<20	582	0.20	<10	34	10	2	96
34	7R18183	0.2	6.65	30	560	5	2.07	<1	2	68	89	1.48	1.25	<10	0.36	285	89	2.58	5	530	24	<5	<20	592	0.20	<10	34	20	2	48
35	7R18184	<0.2	7.53	20	720	<5	2.47	<1	2	78	109	1.76	1.57	<10	0.39	354	89	2.45	5	570	28	<5	<20	583	0.21	<10	40	<10	3	47
36	7R18185	<0.2	6.44	40	1490	5	2.30	<1	1	83	96	1.39	1.65	<10	0.31	315	114	2.30	6	440	26	<5	<20	564	0.18	<10	28	<10	2	51
37	7R18186	<0.2	7.24	50	640	<5	2.20	1	2	89	75	1.58	1.21	<10	0.28	344	176	2.42	6	580	26	<5	<20	521	0.24	<10	34	20	3	95
38	7R18187	<0.2	6.32	10	550	<5	1.91	<1	2	92	73	1.59	0.75	<10	0.42	333	79	2.77	6	570	26	<5	<20	682	0.23	<10	34	<10	3	59
39	7R18188	<0.2	5.94	10	1485	5	0.81	<1	<1	79	120	0.63	3.22	10	0.05	80	241	1.92	3	140	36	<5	<20	290	0.02	<10	5	<10	19	30
40	7R18189	0.7	6.00	25	1380	1435	0.87	1	<1	80	235	0.80	2.88	10	0.05	112	118	1.98	2	140	54	10	<20	231	0.02	<10	4	<10	17	66
41	7R18190	<0.2	6.82	80	535	<5	2.54	<1	1	73	72	1.64	1.05	<10	0.40	329	124	2.73	6	550	28	<5	<20	649	0.22	<10	32	<10	3	57
42	7R18191	<0.2	7.33	10	940	<5	1.81	<1	5	20	122	2.81	3.45	40	0.62	647	652	1.72	17	920	20	<5	<20	371	0.28	<10	49	<10	17	92
43	7R18192	<0.2	6.81	10	610	<5	2.74	<1	2	79	67	1.74	0.86	<10	0.50	391	255	2.83	6	570	24	<5	<20	693	0.25	<10	38	<10	3	64
44	7R18193	<0.2	6.50	10	540	<5	2.75	<1	<1	78	15	1.38	0.72	<10	0.40	279	904	2.73	5	520	22	<5	<20	647	0.21	<10	32	<10	2	45
45	7R18194	<0.2	6.62	10	545	<5	2.78	<1	1	93	47	1.57	0.77	<10	0.42	287	430	2.76	5	550	22	<5	<20	648	0.22	<10	34	<10	2	49
46	7R18195	<0.2	6.90	10	560	<5	2.77	<1	<1	78	38	1.46	0.81	<10	0.42	355	503	2.71	5	530	24	<5	<20	703	0.21	<10	31	<10	2	50
47	7R18196	<0.2	7.66	15	565	<5	2.80	1	1	90	57	1.75	1.13	<10	0.45	397	191	2.92	5	560	28	<5	<20	703	0.23	<10	35	<10	2	156
48	7R18197	<0.2	6.94	10	500	<5	2.76	<1	2	61	36	1.56	0.97	10	0.43	308	148	2.73	5	530	24	<5	<20	679	0.22	<10	32	<10	2	77
49	7R18198	0.2	6.95	15	1740	<5	1.26	1	<1	62	77	0.72	2.83	10	0.12	144	289	2.04	2	200	38	<5	<20	400	0.04	<10	6	<10	16	76
50	7R18199	<0.2	6.45	10	580	<5	2.44	<1	2	89	135	1.74	1.10	<10	0.40	349	106	2.54	5	540	24	<5	<20	601	0.21	<10	34	<10	2	54
51	7R18200	<0.2	6.12	10	420	<5	2.47	<1	2	79	23	1.58	0.91	<10	0.43	366	66	2.91	5	540	24	<5	<20	610	0.24	<10	33	20	3	65
52	7R18201	0.2	5.71	10	1500	<5	0.70	1	<1	64	86	0.69	3.14	10	0.06	116	425	1.97	2	140	40	<5	<20	247	0.02	<10	1	<10	19	144
53	7R18202	0.2	6.65	15	640	10	1.97	<1	2	101	193	1.92	1.62	<10	0.41	333	93	2.36	5	540	26	<5	<20	513	0.19	<10	32	20	4	97
54	7R18203	<0.2	5.46	10	545	<5	2.20	<1	1	111	64	1.52	0.77	<10	0.39	292	492	2.47	5	480	22	<5	<20	556	0.19	<10	28	<10	2	59
55	7R18204	0.7	6.26	20	575	<5	1.47	1	2	97	265	1.82	1.33	<10	0.46	350	123	2.27	5	570	28	<5	<20	549	0.20	<10	33	<10	2	84
56	7R18205	0.2	6.36	10	520	<5	2.43	<1	1	100	186	1.72	0.99	<10	0.42	324	340	2.37	6	560	24	<5	<20	565	0.19	<10	33	<10	2	43
57	7R18206	0.4	6.32	15	555	<5	2.52	<1	1	97	171	1.61	0.89	<10	0.43	300	112	2.70	5	540	24	<5	<20	558	0.21	<10	32	<10	2	49
58	7R18207	0.2	6.19	10	580	<5	2.42	<1	2	73	57	1.55	0.73	<10	0.44	290	157	2.76	5	560	22	<5	<20	659	0.22	<10	31	<10	3	52
59	7R18208	0.4	6.29	10	635	<5	2.69	2	2	93	153	1.71	0.87	<10	0.44	306	52	2.65	6	540	20	<5	<20	628	0.21	<10	33	<10	2	99
60	7R18209	<0.2	6.62	15	590	<5	2.78	<1	2	76	55	1.46	0.82	<10	0.44	296	50	2.82	6	560	22	<5	<20	629	0.23	<10	34	<10	2	57
61	7R18210	0.8	6.23	25	570	<5	2.88	<1	2	88	391	1.53	0.75	<10	0.41	298	32	2.70	5	550	20	<5	<20	630	0.22	<10	33	<10	2	74
62	7R18211	<0.2	6.65	20	620	<5	3.01	<1	2	83	41	1.52	0.81	<10	0.44	310	113	2.88	6	580	22	<5	<20	680	0.24	<10	35	<10	2	56
63	7R18212	0.4	6.62	105	555	<5	2.59	1	2	93	216	1.80	1.10	<10	0.41	316	107	2.58	5	620	26	<5	<20	524	0.21	<10	44	<10	2	68
64	7R18213	0.2	6.73	15	610	<5	3.03	<1	2	87	50	1.55	0.74	<10	0.42	312	173	2.73	5	570	24	<5	<20	673	0.22	<10	36	<10	2	50
65	7R18214	0.4	6.33	10	530	<5	2.93	<1	2	93	224	1.53	0.78	<10	0.40	306	43	2.81	5	560	22	<5	<20	596	0.22	<10	37	<10	2	54


Et #.	Tag #	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	K%	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
66	7R18215	0.8	6.05	10	590	<5	2.67	<1	2	81	436	1.81	0.87	<10	0.48	298	132	2.88	6	660	24	<5	<20	662	0.20	<10	39	<10	2	52
67	7R18216	<0.2	6.61	15	625	<5	2.82	<1	2	82	204	1.88	0.94	<10	0.45	306	434	2.78	6	710	24	<5	<20	613	0.22	<10	38	<10	3	45
68	7R18217	0.4	5.62	10	615	<5	2.23	<1	2	96	323	1.54	0.95	<10	0.41	255	180	2.49	5	490	22	<5	<20	578	0.18	<10	39	<10	2	43
69	7R18218	0.4	6.46	15	625	<5	2.87	<1	3	98	224	1.70	0.86	<10	0.45	327	39	3.04	5	590	22	<5	<20	637	0.24	<10	43	<10	2	62
70	7R18219	0.8	5.81	10	565	<5	2.29	<1	1	74	317	1.59	0.86	<10	0.38	279	202	2.56	4	530	24	<5	<20	532	0.19	<10	35	<10	2	51
71	7R18220	1.3	7.86	15	715	40	2.31	3	3	134	1024	3.22	1.80	<10	0.50	332	101	2.54	7	660	34	<5	<20	601	0.24	<10	43	<10	3	190
72	7R18221	0.5	5.85	10	575	<5	2.34	<1	2	110	220	1.74	1.06	<10	0.38	254	169	2.46	6	510	20	<5	<20	582	0.19	<10	36	<10	2	52
73	7R18222	0.3	6.30	15	565	<5	2.62	<1	2	71	109	1.56	0.96	<10	0.43	324	46	2.81	5	560	20	<5	<20	657	0.22	<10	33	<10	2	53
74	7R18223	0.2	6.69	10	505	<5	2.42	3	2	88	213	2.03	1.38	<10	0.39	332	78	2.54	6	560	24	<5	<20	584	0.23	<10	33	30	2	224
75	7R18224	0.4	8.15	10	770	40	2.24	<1	4	95	174	2.49	2.24	<10	0.46	323	172	2.45	7	610	30	<5	<20	584	0.26	<10	33	<10	3	65
76	7R18225	0.3	6.76	10	530	<5	2.76	<1	2	77	40	1.52	0.77	<10	0.44	351	192	2.76	5	550	24	<5	<20	708	0.23	<10	31	<10	2	53
77	7R18226	0.4	6.80	10	595	<5	2.60	<1	3	81	236	1.93	1.18	<10	0.43	359	71	2.91	6	570	22	<5	<20	645	0.25	<10	35	<10	3	82
78	7R18227	0.6	6.76	10	605	<5	2.57	<1	2	93	209	1.80	0.89	<10	0.44	321	121	2.75	5	550	24	<5	<20	657	0.20	<10	32	<10	2	52
79	7R18228	0.4	6.23	10	550	<5	2.59	<1	2	75	122	1.54	0.78	<10	0.42	322	172	2.89	5	530	20	<5	<20	632	0.21	<10	34	<10	2	53
80	7R18229	0.7	5.62	5	515	<5	2.37	<1	1	99	333	1.34	0.72	<10	0.33	262	60	2.71	5	450	20	<5	<20	595	0.18	<10	26	<10	2	53
81	7R18230	0.2	6.99	10	615	<5	2.79	<1	2	73	29	1.53	0.87	<10	0.46	367	90	2.81	5	550	24	<5	<20	697	0.23	<10	32	<10	2	70
82	7R18231	0.4	6.22	15	560	<5	2.57	<1	2	85	74	1.69	0.97	<10	0.44	439	53	2.64	5	570	28	<5	<20	586	0.24	<10	35	<10	2	90
83	7R18232	0.4	6.48	10	500	<5	2.45	<1	2	74	83	1.64	1.16	<10	0.42	426	56	2.79	5	570	24	<5	<20	574	0.25	<10	36	<10	2	115
84	7R18233	0.2	7.22	10	545	<5	2.81	<1	2	77	47	1.63	0.88	<10	0.45	342	80	2.91	6	570	28	<5	<20	694	0.23	<10	35	<10	3	62
85	7R18234	<0.2	6.97	10	540	<5	2.61	<1	2	70	28	1.49	0.88	<10	0.44	309	126	2.77	5	530	24	<5	<20	660	0.22	<10	34	<10	2	58
86	7R18235	2.4	6.29	30	485	<5	1.81	3	2	86	1345	2.30	1.11	<10	0.36	363	307	2.32	5	540	24	<5	<20	518	0.20	<10	36	<10	2	127
87	7R18236	0.2	5.89	10	545	<5	1.62	<1	<1	70	92	1.56	1.39	<10	0.35	310	463	2.45	5	490	22	<5	<20	514	0.18	<10	35	<10	3	68
88	7R18237	0.2	6.63	25	445	25	0.43	2	<1	63	84	0.63	4.09	<10	0.04	105	238	1.70	2	200	42	<5	<20	189	0.01	<10	4	<10	13	151
89	7R18238	0.2	6.17	15	220	<5	0.45	2	<1	62	49	0.48	3.31	<10	0.04	85	180	1.99	2	180	30	<5	<20	154	0.01	<10	1	<10	12	118
90	7R18239	0.4	6.13	30	205	<5	0.39	2	<1	64	119	0.53	3.05	<10	0.03	78	354	2.07	2	180	26	<5	<20	111	0.01	<10	2	<10	10	121
91	7R18240	0.2	6.18	40	165	5	0.39	2	<1	65	71	0.57	3.42	<10	0.03	82	317	2.06	2	170	28	<5	<20	100	<0.01	<10	1	<10	11	142
92	7R18241	0.2	5.68	20	160	<5	0.33	3	<1	61	68	0.58	3.21	<10	0.03	70	237	2.01	2	170	24	<5	<20	98	0.01	<10	<1	<10	10	160
93	7R18242	<0.2	6.50	30	135	<5	0.40	2	<1	62	121	0.73	3.46	<10	0.04	84	162	2.15	2	180	32	<5	<20	94	0.01	<10	1	<10	11	124
94	7R18243	<0.2	6.38	30	160	<5	0.38	5	<1	69	166	0.87	3.36	<10	0.04	90	88	1.91	2	170	26	<5	<20	105	0.01	<10	2	<10	8	247

QC DATA:**Repeat:**


1	7R18150	0.4	7.04	10	620	300	2.65	<1	2	94	230	1.67	0.88	<10	0.43	299	113	2.56	6	580	36	<5	<20	682	0.22	<10	32	20	2	66
10	7R18159	<0.2	6.45	15	500	<5	2.79	<1	2	72	40	1.39	0.86	<10	0.40	313	24	2.80	6	510	30	<5	<20	661	0.24	<10	32	20	3	76
19	7R18168	<0.2	6.50	10	630	<5	2.65	<1	2	80	32	1.46	0.78	<10	0.42	307	64	2.74	4	540	26	<5	<20	678	0.23	<10	35	20	2	59
36	7R18185	<0.2	6.47	40	1525	10	2.46	<1	1	88	105	1.46	1.72	<10	0.34	325	118	2.47	5	440	26	<5	<20	567	0.18	<10	27	<10	2	49
40	7R18189	<0.2	0.20	45	45	1610	0.59	1	1	87	222	0.72	2.83	<10	<0.01	77	109	0.05	1	30	40	10	<20	37	<0.01	<10	<1	<10	9	56
45	7R18194	<0.2	6.89	10	585	<5	2.68	<1	1	93	49	1.57	0.78	<10	0.45	298	440	2.85	5	570	22	<5	<20	674	0.23	<10	34	<10	2	50
54	7R18203	<0.2	5.74	10	490	<5	2.44	<1	1	94	58	1.36	0.69	<10	0.35	280	443	2.25	5	440	22	<5	<20	548	0.17	<10	24	<10	2	60
71	7R18220	1.4	8.30	15	735	50	2.18	3	3	127	1014	3.17	1.85	<10	0.50	307	97	2.36	6	620	30	<5	<20	616	0.22	<10	45	<10	3	167
80	7R18229	0.7	5.86	10	515	<5	2.37	<1	1	98	332	1.36	0.72	<10	0.31	267	61	2.83	4	470	22	<5	<20	571	0.18	<10	26	<10	2	62

El #.	Tag #	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	K%	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn	
Resplit:																															
1	7R18 150	0.4	6.93	10	625	300	2.46	<1	2	81	228	1.54	0.95	<10	0.40	260	48	2.74	5	540	30	<5	<20	667	0.20	<10	33	20	3	61	
36	7R18 185	<0.2	6.00	45	1615	5	1.89	<1	1	81	102	1.19	1.75	<10	0.28	276	97	2.24	4	390	24	<5	<20	558	0.15	<10	23	<10	2	46	
71	7R18 220	1.1	7.90	10	715	30	2.33	2	2	131	985	3.25	1.78	<10	0.44	336	103	2.56	5	580	34	<5	<20	600	0.22	<10	39	<10	2	168	
Standard:																															
STSD - 3		0.4	5.68	25	1425	<5	2.48	1	17	62	39	4.23	1.32	40	1.31	2676	5	1.06	32	1730	58	<5	<20	276	0.37	<10	118	<10	33	210	
STSD - 3		0.4	5.84	30	1445	<5	2.65	1	17	62	42	4.30	1.39	40	1.43	2526	6	1.11	35	1790	52	<5	<20	263	0.38	<10	120	<10	30	220	
STSD - 3		0.5	5.74	25	1420	<5	2.54	1	17	63	42	4.22	1.39	40	1.31	2554	6	1.19	32	1660	56	<5	<20	270	0.37	<10	122	<10	32	208	

JJ/jj
 01-1624
 XLS:07

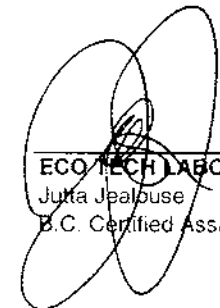

ECO TECH LABORATORY LTD.
 Jutta Jealouse
 B.C. Certified Assayer

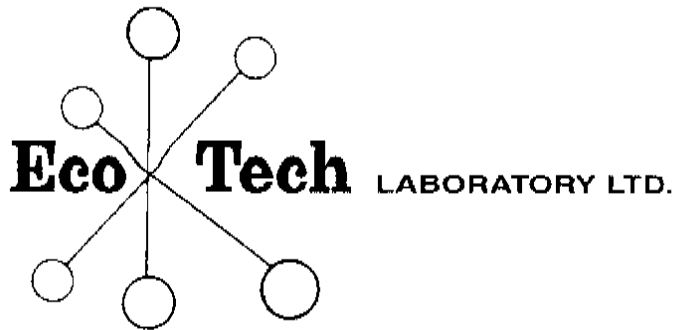

ASSAYING, GEOCHEMISTRY
ANALYTICAL CHEMISTRY
ENVIRONMENTAL TESTING
ISO 9001 Accredited Co.

10041 Dallas Drive, Kamloops, BC V2C 6T4
Phone (250) 573-5700 Fax (250) 573-4557
E-mail: info@ecotechlab.com
www.ecotechlab.com

CERTIFICATE OF ASSAY AK 2007-1623

Pacific Cascade Resources
520 - 700 W. Pender Street
Vancouver, BC
V6C 1G8

13-Nov-07

No. of samples received: 140
Sample Type: Core
Project: Crack Moly
Submitted by: Mike

ET #.	Tag #	Mo (%)
13	7R18013	0.050
14	7R18014	0.064
37	7R18037	0.106
41	7R18041	0.064
72	7R18072	0.063
82	7R18082	0.064
132	7R18132	0.050
139	7R18139	0.067

QC DATA:


Repeat:

13 7R18013 0.051

Standards:

MP2 0.285
MP2 0.282

JJ/jl
XLS/07

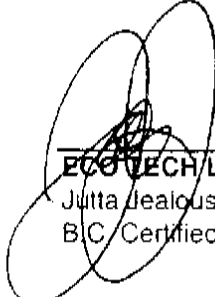
Eco Tech LABORATORY LTD.
Jutta Jealous
B.C. Certified Assayer

ECO TECH LABORATORY LTD.

10041 Dallas Drive

KAMLOOPS, B.C.

V2C 6T4

ICP CERTIFICATE OF ANALYSIS AK 2007- 1623

Pacific Cascade Resources

520 - 700 W. Pender Street

Vancouver, BC

V6C 1G8

Phone: 250-573-5700

Fax : 250-573-4557

No. of samples received: 140

Sample Type: Core

Project: Crack Moly

Submitted by: Mike

Values in ppm unless otherwise reported

Et #.	Tag #	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	K%	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
1	7R18001	1.4	6.04	10	455	100	2.38	<1	1	49	53	1.33	0.88	<10	0.29	323	50	2.20	5	480	26	<5	<20	420	0.19	<10	24	<10	3	58
2	7R18002	0.6	7.45	15	720	15	2.01	<1	2	60	47	1.55	1.09	<10	0.26	327	19	2.06	5	540	26	<5	<20	460	0.22	<10	28	<10	3	66
3	7R18003	1.0	6.59	10	525	<5	2.64	1	2	85	32	1.52	0.74	<10	0.41	317	20	2.97	6	530	30	<5	<20	635	0.22	<10	28	<10	3	122
4	7R18004	1.1	6.34	5	575	<5	2.52	11	2	48	97	1.50	0.83	<10	0.45	286	56	2.75	5	510	22	<5	<20	623	0.21	<10	30	<10	2	342
5	7R18005	0.6	6.48	5	530	<5	2.41	2	2	77	24	1.38	0.69	<10	0.40	294	16	3.03	5	470	20	<5	<20	632	0.20	<10	27	<10	3	121
6	7R18006	<0.2	6.64	5	580	<5	2.67	<1	2	87	16	1.44	0.73	<10	0.45	299	120	2.96	6	480	24	<5	<20	656	0.22	<10	29	<10	3	55
7	7R18007	0.6	6.11	5	570	<5	2.59	<1	2	94	13	1.48	0.90	<10	0.42	322	252	2.68	6	480	28	<5	<20	581	0.22	<10	28	<10	3	76
8	7R18008	2.0	6.85	5	565	<5	2.61	<1	2	63	16	1.44	0.73	<10	0.44	305	33	2.88	5	510	26	<5	<20	657	0.22	<10	28	<10	3	92
9	7R18009	3.0	6.87	5	535	<5	2.67	<1	2	80	31	1.50	0.71	<10	0.45	322	77	2.90	7	520	24	<5	<20	657	0.21	<10	29	<10	3	83
10	7R18010	8.6	6.59	5	545	<5	2.44	2	2	66	66	1.52	0.85	<10	0.44	325	21	2.84	6	480	26	<5	<20	616	0.20	<10	29	<10	2	169
11	7R18011	0.2	6.80	5	565	<5	2.75	<1	2	81	21	1.55	0.76	10	0.43	337	11	2.98	7	520	24	<5	<20	645	0.23	<10	29	<10	2	78
12	7R18012	0.7	6.30	10	425	<5	2.41	4	1	68	60	1.47	0.80	<10	0.35	290	58	2.94	5	560	22	<5	<20	546	0.20	<10	30	<10	2	202
13	7R18013	0.8	6.02	10	440	<5	2.11	7	1	99	83	1.54	0.91	<10	0.35	303	507	2.60	6	850	22	<5	<20	506	0.19	<10	28	<10	3	267
14	7R18014	0.2	7.52	10	880	<5	1.85	<1	6	20	133	2.92	2.65	30	0.60	697	656	1.86	19	910	28	<5	<20	340	0.28	<10	44	<10	15	100
15	7R18015	1.4	6.58	5	550	<5	2.84	<1	2	77	16	1.60	0.74	<10	0.45	309	27	3.05	6	520	24	<5	<20	624	0.23	<10	33	<10	3	100
16	7R18016	2.4	6.67	5	540	<5	2.73	6	2	67	40	1.50	0.82	<10	0.43	311	51	2.77	5	510	26	<5	<20	606	0.21	<10	30	<10	3	258
17	7R18017	3.6	6.63	10	500	<5	2.66	2	2	64	41	1.54	0.76	<10	0.41	334	65	2.80	6	490	26	<5	<20	598	0.22	<10	30	<10	3	161
18	7R18018	0.8	6.46	10	415	<5	2.80	1	2	83	18	1.53	0.70	<10	0.37	321	23	2.92	6	510	20	<5	<20	567	0.23	<10	31	<10	3	92
19	7R18019	3.0	6.89	5	545	<5	2.79	<1	2	73	15	1.46	0.76	<10	0.43	360	69	3.03	5	500	22	<5	<20	651	0.22	<10	30	<10	3	67
20	7R18020	<0.2	6.21	5	420	<5	2.09	<1	2	74	32	1.19	0.85	<10	0.33	306	85	2.92	4	410	24	<5	<20	500	0.16	<10	23	<10	2	62
21	7R18021	2.4	6.78	10	460	<5	2.85	<1	2	75	62	1.56	0.92	<10	0.38	421	119	2.76	6	510	24	<5	<20	585	0.22	<10	31	<10	3	96
22	7R18022	1.7	7.24	10	560	<5	2.81	4	2	82	156	1.66	0.98	<10	0.45	355	76	2.75	5	530	26	<5	<20	618	0.23	<10	31	<10	3	348
23	7R18023	3.4	6.44	10	570	<5	2.50	2	3	75	780	1.75	1.03	<10	0.42	342	113	2.44	5	510	24	<5	<20	588	0.20	<10	32	<10	3	116
24	7R18024	0.8	6.40	20	535	<5	2.11	<1	2	78	258	1.58	0.99	<10	0.38	294	75	2.45	5	490	24	<5	<20	512	0.19	<10	31	<10	3	59
25	7R18025	1.6	7.23	10	555	<5	2.82	<1	2	70	31	1.64	0.75	<10	0.47	335	68	2.95	6	520	26	<5	<20	663	0.24	<10	30	<10	3	61


Et #.	Tag #	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	K%	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
26	7R18026	0.2	6.60	5	490	<5	2.65	<1	2	78	51	1.52	0.74	<10	0.42	299	17	2.88	5	500	22	<5	<20	633	0.21	<10	29	<10	3	52
27	7R18027	<0.2	6.49	5	540	<5	2.49	<1	3	74	64	1.71	0.88	<10	0.44	306	23	2.56	6	480	24	<5	<20	618	0.22	<10	30	<10	3	109
28	7R18028	0.4	7.20	10	555	<5	2.81	<1	3	101	53	1.70	0.90	<10	0.43	308	38	2.82	6	530	22	<5	<20	661	0.23	<10	30	<10	3	66
29	7R18029	4.2	7.03	5	540	<5	2.77	<1	2	67	27	1.43	0.77	<10	0.44	314	8	2.91	6	480	24	<5	<20	684	0.21	<10	27	<10	3	92
30	7R18030	1.4	6.43	10	470	<5	2.51	1	2	81	567	1.56	0.70	<10	0.38	283	33	2.67	5	500	20	<5	<20	560	0.22	<10	32	<10	2	93
31	7R18031	3.2	6.91	5	535	<5	2.71	<1	2	68	44	1.51	0.78	10	0.44	316	44	2.91	6	520	26	<5	<20	642	0.22	<10	30	<10	3	82
32	7R18032	2.0	7.95	10	570	<5	3.20	<1	3	63	53	1.76	0.83	<10	0.49	351	30	3.07	5	580	26	<5	<20	682	0.26	<10	32	<10	3	66
33	7R18033	3.4	6.27	10	515	<5	2.68	<1	2	69	82	1.49	0.78	<10	0.41	291	48	2.64	4	490	20	<5	<20	611	0.20	<10	29	<10	2	103
34	7R18034	0.2	6.88	10	580	<5	3.05	<1	2	65	18	1.46	0.72	<10	0.43	291	114	3.01	4	500	24	<5	<20	678	0.22	<10	31	<10	3	63
35	7R18035	0.6	6.86	5	590	<5	2.96	<1	2	66	19	1.55	0.78	<10	0.45	287	60	2.83	6	510	22	<5	<20	672	0.23	<10	32	<10	3	104
36	7R18036	<0.2	6.75	10	520	<5	2.79	<1	2	85	54	1.61	0.82	<10	0.42	333	137	2.85	6	520	22	<5	<20	641	0.22	<10	31	<10	2	108
37	7R18037	1.1	6.29	5	440	<5	2.35	<1	1	99	49	1.42	0.70	<10	0.37	263	1088	2.52	5	420	20	<5	<20	522	0.19	<10	24	<10	2	129
38	7R18038	1.2	6.80	10	545	<5	2.63	4	3	69	166	1.76	1.00	<10	0.43	404	35	2.87	5	510	22	<5	<20	595	0.23	<10	33	<10	2	377
39	7R18039	0.6	6.58	50	550	20	2.48	1	3	77	216	1.70	0.97	<10	0.39	309	45	2.28	5	460	24	<5	<20	534	0.20	<10	34	<10	2	128
40	7R18040	<0.2	7.55	10	620	<5	3.02	2	3	62	41	1.73	0.83	<10	0.49	340	19	3.01	7	550	26	<5	<20	695	0.25	<10	33	<10	3	174
41	7R18041	<0.2	7.72	10	870	<5	1.99	<1	6	20	129	2.98	2.48	30	0.59	687	655	1.85	19	940	28	<5	<20	332	0.29	<10	44	<10	16	99
42	7R18042	1.3	6.71	10	655	<5	2.81	<1	2	67	23	1.68	0.83	<10	0.51	324	30	2.94	7	580	22	<5	<20	652	0.27	<10	36	<10	3	87
43	7R18043	<0.2	7.05	10	540	<5	2.76	<1	2	54	121	1.72	0.86	<10	0.46	357	89	2.87	5	500	24	<5	<20	657	0.22	<10	30	<10	2	73
44	7R18044	<0.2	5.51	5	445	<5	2.45	3	3	69	110	1.59	0.88	<10	0.37	322	234	2.65	6	490	18	<5	<20	495	0.21	<10	29	<10	2	206
45	7R18045	<0.2	6.39	5	510	<5	2.84	<1	2	64	63	1.51	0.73	<10	0.42	351	18	3.00	5	520	20	<5	<20	612	0.22	<10	30	<10	2	65
46	7R18046	<0.2	6.45	10	520	<5	2.84	<1	3	79	133	1.65	0.88	<10	0.44	390	50	2.91	5	520	22	<5	<20	617	0.23	<10	32	<10	2	107
47	7R18047	0.2	6.26	10	470	<5	2.73	<1	2	69	154	1.58	0.80	<10	0.42	337	32	2.72	5	490	20	<5	<20	601	0.20	<10	28	<10	2	54
48	7R18048	<0.2	6.25	5	465	<5	2.81	<1	2	65	74	1.54	0.78	<10	0.40	389	15	2.87	5	520	22	<5	<20	604	0.24	<10	31	<10	2	123
49	7R18049	<0.2	6.11	5	495	<5	2.75	<1	3	68	143	1.63	0.87	<10	0.43	412	68	2.84	6	490	20	<5	<20	591	0.22	<10	31	<10	2	127
50	7R18050	<0.2	6.09	5	480	<5	2.74	1	2	56	69	1.50	0.75	<10	0.42	437	31	2.89	5	500	18	<5	<20	593	0.24	<10	30	<10	2	132
51	7R18051	0.5	5.82	5	460	<5	2.47	1	2	55	279	1.78	0.87	<10	0.36	329	42	2.65	5	530	18	<5	<20	508	0.21	<10	31	<10	2	144
52	7R18052	<0.2	5.50	10	455	<5	2.38	<1	2	66	52	1.46	0.84	<10	0.34	254	470	2.59	5	490	16	<5	<20	491	0.21	<10	31	<10	2	66
53	7R18053	1.1	6.35	10	550	<5	2.62	<1	2	57	112	1.60	0.82	<10	0.42	345	44	2.83	4	500	22	<5	<20	599	0.22	<10	32	<10	2	102
54	7R18054	<0.2	7.04	10	655	<5	2.29	<1	1	66	7	1.07	0.79	<10	0.27	163	<1	3.24	4	280	26	<5	<20	620	0.15	<10	14	<10	2	58
55	7R18055	<0.2	6.24	5	475	<5	2.54	<1	2	53	102	1.69	0.96	<10	0.41	313	65	2.87	6	520	22	<5	<20	587	0.23	<10	34	<10	2	102
56	7R18056	1.4	6.41	15	545	<5	2.00	9	2	74	940	2.03	1.24	<10	0.41	268	177	2.25	5	450	20	<5	<20	511	0.20	<10	31	<10	2	502
57	7R18057	<0.2	6.33	5	540	<5	2.63	<1	3	58	54	1.62	0.89	<10	0.46	344	94	2.85	5	510	20	<5	<20	600	0.23	<10	31	<10	2	92
58	7R18058	<0.2	6.09	5	510	<5	2.66	<1	2	65	81	1.53	0.83	<10	0.42	317	67	2.91	5	510	20	<5	<20	601	0.22	<10	31	<10	2	78
59	7R18059	0.2	6.37	10	560	<5	2.57	3	3	65	175	1.72	1.01	<10	0.44	342	71	2.77	5	500	24	<5	<20	574	0.23	<10	32	<10	2	253
60	7R18060	<0.2	6.75	10	545	<5	2.79	<1	3	66	13	1.56	0.80	<10	0.44	305	37	2.81	6	520	22	<5	<20	632	0.23	<10	31	<10	3	61
61	7R18061	0.2	5.67	5	485	<5	2.87	<1	2	65	30	1.45	0.73	<10	0.42	278	44	2.87	5	480	18	<5	<20	602	0.21	<10	30	<10	2	61
62	7R18062	10.4	5.98	5	545	<5	2.72	<1	2	68	22	1.40	0.81	<10	0.42	347	14	2.94	6	490	22	<5	<20	620	0.22	<10	32	<10	2	101
63	7R18063	0.6	6.47	10	530	<5	2.44	<1	3	64	300	1.88	1.13	<10	0.42	323	80	2.53	6	520	20	<5	<20	555	0.21	<10	34	<10	2	65
64	7R18064	<0.2	5.95	5	490	<5	2.66	<1	2	75	41	1.48	0.76	<10	0.40	327	66	2.86	5	500	22	<5	<20	583	0.22	<10	33	<10	2	70
65	7R18065	0.4	5.54	5	500	<5	2.84	<1	2	66	31	1.42	0.70	<10	0.38	323	76	3.05	6	500	20	<5	<20	558	0.23	<10	33	<10	1	75


Et #.	Tag #	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	K%	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
66	7R18066	0.6	6.10	5	540	<5	2.77	<1	2	75	27	1.53	0.77	<10	0.42	336	34	2.96	5	510	22	<5	<20	588	0.24	<10	31	<10	3	126
67	7R18067	0.4	6.12	5	515	<5	2.92	<1	2	70	211	1.56	0.88	<10	0.39	338	52	2.96	7	540	22	<5	<20	480	0.24	<10	38	<10	2	75
68	7R18068	<0.2	6.29	10	530	<5	2.85	<1	3	65	7	1.46	0.71	<10	0.38	311	47	3.00	6	510	20	<5	<20	577	0.24	<10	35	<10	2	81
69	7R18069	0.4	6.33	5	535	<5	2.84	<1	2	79	22	1.48	0.77	<10	0.42	328	59	2.93	5	500	22	<5	<20	594	0.22	<10	32	<10	2	103
70	7R18070	<0.2	5.59	5	510	<5	2.81	<1	2	82	34	1.38	0.78	<10	0.34	310	39	2.97	5	460	20	<5	<20	549	0.20	<10	30	<10	2	69
71	7R18071	0.2	5.74	5	485	<5	2.69	<1	2	53	107	1.37	0.74	<10	0.35	290	21	3.03	3	460	22	<5	<20	515	0.21	<10	30	<10	1	65
72	7R18072	<0.2	6.55	10	895	<5	1.69	<1	6	19	131	2.68	2.65	30	0.59	635	631	1.55	17	870	22	<5	<20	340	0.28	<10	47	<10	15	96
73	7R18073	0.2	6.33	<5	535	<5	2.58	<1	2	85	36	1.51	0.89	<10	0.39	286	54	2.77	5	500	22	<5	<20	553	0.22	<10	30	<10	2	93
74	7R18074	0.2	5.82	5	490	<5	2.64	<1	2	79	20	1.44	0.71	<10	0.36	257	88	2.96	5	470	20	<5	<20	550	0.22	<10	31	<10	2	54
75	7R18075	<0.2	6.10	5	545	<5	2.64	<1	2	69	24	1.52	0.82	<10	0.40	298	148	2.97	5	500	20	<5	<20	571	0.22	<10	29	<10	2	62
76	7R18076	<0.2	6.37	5	550	<5	2.72	<1	2	63	33	1.47	0.77	<10	0.41	323	25	2.80	5	490	22	<5	<20	600	0.23	<10	28	<10	2	68
77	7R18077	<0.2	5.79	5	535	<5	2.61	2	2	77	86	1.54	0.86	<10	0.37	300	28	2.70	5	480	20	<5	<20	542	0.21	<10	34	<10	2	152
78	7R18078	0.6	5.37	25	480	<5	2.42	<1	2	67	254	1.46	0.81	<10	0.34	276	31	2.56	5	510	20	<5	<20	488	0.20	<10	36	<10	2	95
79	7R18079	<0.2	5.21	5	470	10	2.52	<1	2	72	26	1.30	0.78	<10	0.35	276	68	2.73	4	500	16	<5	<20	478	0.21	<10	33	<10	2	77
80	7R18080	<0.2	5.83	<5	535	<5	2.45	3	2	69	99	1.72	1.03	<10	0.40	340	45	2.53	5	510	20	<5	<20	505	0.23	<10	32	<10	2	274
81	7R18081	<0.2	6.19	<5	550	<5	2.80	<1	2	71	10	1.49	0.77	<10	0.43	302	64	2.92	5	500	20	<5	<20	584	0.23	<10	30	<10	2	59
82	7R18082	0.2	6.57	10	860	<5	1.69	<1	6	19	129	2.72	2.54	30	0.58	618	632	1.66	17	880	20	<5	<20	323	0.27	<10	46	<10	15	90
83	7R18083	<0.2	6.33	10	580	<5	2.82	<1	2	68	10	1.52	0.82	<10	0.41	304	35	3.03	5	500	22	<5	<20	572	0.24	<10	33	<10	2	68
84	7R18084	<0.2	6.27	5	575	<5	2.74	<1	2	72	7	1.46	0.86	<10	0.41	277	37	2.83	4	470	22	<5	<20	578	0.22	<10	31	<10	2	52
85	7R18085	0.2	5.52	5	695	<5	1.86	<1	1	76	108	1.07	1.19	<10	0.22	196	212	2.61	4	350	20	<5	<20	462	0.12	<10	19	<10	2	32
86	7R18086	<0.2	6.06	5	545	<5	2.69	<1	2	66	29	1.36	0.72	<10	0.39	286	69	2.88	4	480	22	<5	<20	580	0.22	<10	30	<10	2	65
87	7R18087	<0.2	6.15	5	595	<5	2.71	<1	2	72	22	1.41	0.77	<10	0.43	265	18	2.96	4	520	24	<5	<20	602	0.23	<10	32	<10	2	76
88	7R18088	0.6	6.57	5	590	<5	2.76	<1	2	69	71	1.56	0.80	<10	0.42	341	46	2.93	5	510	20	<5	<20	595	0.23	<10	33	<10	2	107
89	7R18089	<0.2	6.45	10	605	<5	2.53	<1	2	57	120	1.50	0.90	10	0.42	274	34	2.67	8	490	22	<5	<20	556	0.21	<10	32	<10	2	71
90	7R18090	<0.2	6.68	10	590	<5	2.71	<1	2	70	52	1.55	0.78	<10	0.45	299	118	2.82	5	540	20	<5	<20	597	0.23	<10	32	<10	2	67
91	7R18091	<0.2	6.33	5	580	<5	2.69	<1	3	63	17	1.47	0.79	<10	0.41	265	22	2.84	6	490	20	<5	<20	573	0.23	<10	31	<10	2	66
92	7R18092	0.4	6.22	10	550	<5	2.39	<1	2	77	148	1.54	0.91	<10	0.39	269	100	2.63	5	450	18	<5	<20	521	0.19	<10	27	<10	2	52
93	7R18093	<0.2	5.53	5	540	<5	2.59	<1	2	50	124	1.41	0.84	<10	0.37	290	36	3.11	5	450	20	<5	<20	535	0.21	<10	28	<10	2	108
94	7R18094	0.2	6.22	10	590	<5	2.41	2	2	62	192	1.57	0.99	<10	0.37	300	34	2.78	5	450	20	<5	<20	539	0.20	<10	29	<10	2	167
95	7R18095	0.2	7.40	15	1005	<5	1.63	1	4	46	376	2.40	2.28	<10	0.43	311	60	1.86	4	490	24	<5	<20	474	0.18	<10	33	<10	2	99
96	7R18096	0.2	6.77	10	585	<5	2.63	2	2	52	85	1.53	0.93	<10	0.39	296	72	2.86	5	490	24	<5	<20	594	0.21	<10	27	<10	2	180
97	7R18097	0.5	6.46	10	635	<5	2.53	1	2	66	78	1.67	1.13	<10	0.39	339	53	2.63	5	490	24	<5	<20	548	0.22	<10	30	<10	2	159
98	7R18098	1.6	6.17	25	520	<5	2.68	4	3	71	994	2.11	1.11	<10	0.34	352	44	2.75	4	500	22	<5	<20	503	0.21	<10	33	<10	2	271
99	7R18099	0.4	5.90	80	510	<5	2.65	1	2	60	161	1.53	0.93	<10	0.33	286	36	2.81	5	500	20	<5	<20	466	0.21	<10	31	<10	2	87
100	7R18100	<0.2	6.49	10	710	<5	2.02	<1	3	69	102	1.93	1.79	<10	0.45	320	253	2.28	4	510	24	<5	<20	471	0.22	<10	34	<10	2	102
101	7R18101	0.4	6.57	10	575	<5	2.65	2	2	39	360	1.58	0.88	<10	0.40	269	55	3.01	4	500	24	<5	<20	591	0.21	<10	29	<10	2	126
102	7R18102	0.4	5.59	15	545	<5	2.55	2	2	55	195	1.38	0.91	<10	0.35	251	135	2.80	5	470	20	<5	<20	501	0.21	<10	32	<10	2	132
103	7R18103	<0.2	5.81	10	560	<5	2.52	3	2	64	61	1.46	0.89	<10	0.37	271	52	2.82	5	500	20	<5	<20	518	0.21	<10	29	<10	2	231
104	7R18104	<0.2	5.93	10	570	<5	2.77	<1	2	68	18	1.46	0.79	<10	0.37	223	146	3.11	4	490	20	<5	<20	540	0.23	<10	33	<10	2	49
105	7R18105	<0.2	6.45	5	575	<5	2.86	<1	2	67	22	1.48	0.95	<10	0.40	273	42	3.00	5	540	22	<5	<20	566	0.23	<10	30	<10	2	56

Et #.	Tag #	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	K%	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
106	7R18106	<0.2	7.05	<5	610	<5	2.82	<1	2	66	10	1.45	0.79	<10	0.42	238	47	3.15	5	510	24	<5	<20	691	0.23	<10	32	<10	1	49
107	7R18107	<0.2	7.41	<5	605	<5	2.69	<1	2	81	22	1.48	0.87	<10	0.40	238	85	3.01	5	490	26	<5	<20	680	0.22	<10	29	<10	2	52
108	7R18108	<0.2	7.21	5	605	<5	2.77	<1	2	102	19	1.44	0.75	<10	0.41	216	35	3.23	6	520	26	<5	<20	715	0.22	<10	30	<10	2	51
109	7R18109	<0.2	6.80	5	610	<5	2.77	<1	2	71	20	1.41	0.76	<10	0.41	254	49	3.04	5	500	22	<5	<20	696	0.23	<10	30	<10	2	64
110	7R18110	<0.2	6.91	<5	600	<5	2.64	<1	2	96	43	1.46	0.76	<10	0.38	251	17	2.97	6	510	22	<5	<20	677	0.22	<10	27	<10	2	55
111	7R18111	<0.2	6.91	5	565	<5	2.33	<1	2	91	26	1.43	0.70	<10	0.41	253	211	2.88	7	540	24	<5	<20	679	0.22	<10	28	<10	2	53
112	7R18112	<0.2	6.89	5	595	<5	2.75	<1	2	82	20	1.40	0.69	<10	0.40	260	37	3.00	5	510	24	<5	<20	680	0.22	<10	27	<10	2	53
113	7R18113	0.4	7.31	10	575	<5	2.58	11	3	72	188	1.72	1.14	<10	0.35	261	8	2.76	6	520	26	<5	<20	577	0.22	<10	31	<10	2	387
114	7R18114	<0.2	7.38	<5	615	<5	2.60	<1	2	92	28	1.59	0.82	<10	0.42	292	322	3.16	5	540	28	<5	<20	682	0.23	<10	30	<10	2	52
115	7R18115	0.2	7.34	<5	890	20	2.00	<1	1	97	75	1.26	1.65	<10	0.28	229	21	2.72	5	380	30	<5	<20	542	0.15	<10	19	<10	8	49
116	7R18116	<0.2	7.40	<5	635	<5	2.66	<1	2	93	22	1.52	0.80	<10	0.41	271	15	3.14	5	520	28	<5	<20	709	0.23	<10	30	<10	2	56
117	7R18117	<0.2	7.04	5	605	<5	2.87	<1	2	84	36	1.55	0.81	<10	0.38	284	46	3.17	5	540	24	<5	<20	662	0.23	<10	29	<10	2	87
118	7R18118	<0.2	6.81	5	625	<5	2.74	<1	2	97	12	1.42	0.80	<10	0.38	224	55	3.19	4	520	24	<5	<20	681	0.23	<10	29	<10	2	52
119	7R18119	<0.2	6.95	5	650	<5	2.32	<1	2	94	47	1.56	0.87	<10	0.41	326	198	3.02	6	560	28	<5	<20	687	0.24	<10	33	<10	2	53
120	7R18120	0.2	7.25	5	605	<5	2.65	<1	2	87	59	1.55	0.85	<10	0.41	318	53	3.11	5	510	26	<5	<20	705	0.23	<10	31	<10	2	82
121	7R18121	<0.2	7.19	<5	595	<5	2.85	<1	2	80	38	1.50	0.81	<10	0.42	267	60	3.32	6	520	24	<5	<20	720	0.23	<10	31	<10	2	55
122	7R18122	<0.2	7.06	5	570	<5	2.06	<1	2	87	96	1.60	0.78	<10	0.42	302	167	3.08	5	540	26	<5	<20	710	0.24	<10	31	<10	2	60
123	7R18123	<0.2	7.31	5	615	<5	2.91	1	2	87	41	1.56	0.77	<10	0.43	275	26	3.20	6	540	24	<5	<20	689	0.23	<10	27	<10	2	129
124	7R18124	<0.2	7.66	5	635	<5	3.01	<1	2	91	31	1.50	0.76	<10	0.43	280	140	3.26	5	530	24	<5	<20	734	0.23	<10	26	<10	2	54
125	7R18125	<0.2	6.81	<5	565	<5	2.85	<1	2	90	47	1.48	0.79	<10	0.39	270	73	2.91	6	500	22	<5	<20	663	0.22	<10	28	<10	2	56
126	7R18126	<0.2	7.33	5	625	<5	2.97	<1	2	92	41	1.57	0.79	<10	0.41	255	23	3.08	6	510	26	<5	<20	713	0.23	<10	29	<10	2	63
127	7R18127	<0.2	7.67	<5	670	<5	2.81	<1	2	82	79	1.69	0.98	<10	0.42	254	78	3.14	5	530	24	<5	<20	664	0.22	<10	31	<10	2	67
128	7R18128	<0.2	7.23	5	625	<5	2.49	<1	2	97	71	1.57	0.82	<10	0.42	278	57	3.02	6	510	22	<5	<20	704	0.22	<10	31	<10	2	52
129	7R18129	<0.2	6.96	5	585	<5	2.37	<1	2	93	47	1.57	0.73	<10	0.40	297	30	3.03	6	530	24	<5	<20	677	0.23	<10	30	<10	2	50
130	7R18130	<0.2	7.37	20	680	<5	2.39	<1	2	106	76	1.57	0.86	<10	0.40	337	168	2.98	6	550	24	<5	<20	634	0.23	<10	31	<10	2	47
131	7R18131	<0.2	6.78	5	590	<5	2.35	<1	2	91	45	1.61	0.72	<10	0.42	301	198	3.12	6	520	24	<5	<20	676	0.22	<10	30	<10	2	51
132	7R18132	<0.2	6.83	45	610	<5	2.40	<1	2	99	41	1.62	0.76	<10	0.44	311	488	3.01	7	520	22	<5	<20	650	0.23	<10	31	<10	2	64
133	7R18133	<0.2	7.46	5	620	<5	2.28	<1	2	80	30	1.56	0.76	<10	0.42	293	102	2.97	6	550	26	<5	<20	723	0.23	<10	30	<10	2	54
134	7R18134	<0.2	7.06	<5	600	<5	2.31	<1	2	101	40	1.54	0.79	<10	0.40	277	33	3.03	6	510	24	<5	<20	709	0.22	<10	31	<10	2	47
135	7R18135	<0.2	6.76	<5	545	<5	2.24	<1	1	84	93	1.61	0.80	<10	0.38	302	49	3.03	6	520	24	<5	<20	651	0.21	<10	29	<10	2	47
136	7R18136	<0.2	7.75	5	550	<5	2.39	<1	2	87	331	2.32	1.28	<10	0.44	332	45	3.06	6	620	26	<5	<20	607	0.22	<10	38	<10	2	46
137	7R18137	<0.2	7.36	10	540	<5	2.74	<1	2	81	56	1.59	0.84	<10	0.39	308	8	3.16	6	540	26	<5	<20	685	0.22	<10	28	<10	2	42
138	7R18138	<0.2	6.88	5	535	30	2.53	<1	2	99	146	1.68	0.96	<10	0.35	291	102	2.94	5	540	24	<5	<20	602	0.20	<10	28	<10	3	44
139	7R18139	<0.2	7.19	40	490	45	2.18	<1	1	106	146	1.89	1.09	<10	0.33	311	641	2.89	6	570	26	<5	<20	591	0.20	<10	33	<10	3	49
140	7R18140	<0.2	7.19	45	790	<5	0.79	<1	<1	71	144	1.05	3.31	<10	0.12	106	44	1.24	2	240	32	<5	<20	267	0.03	<10	5	<10	18	25

Et #.	Tag #	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	K%	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn	
QC DATA:																															
<i>Repeat:</i>																															
1	7R18001	2.0	6.39	10	495	85	2.47	<1	2	52	59	1.47	0.99	<10	0.32	340	52	2.31	5	500	24	<5	<20	457	0.20	<10	26	<10	3	62	
10	7R18010	7.9	6.88	5	555	<5	2.67	2	2	71	68	1.56	0.89	<10	0.44	345	20	2.76	6	490	26	<5	<20	629	0.21	<10	29	<10	3	163	
19	7R18019	2.7	6.84	5	540	<5	2.78	<1	2	73	14	1.46	0.75	10	0.43	368	70	2.92	5	500	24	<5	<20	650	0.22	<10	30	<10	3	64	
36	7R18036	<0.2	6.49	5	535	<5	2.72	<1	2	88	54	1.64	0.87	<10	0.42	331	136	2.90	6	520	20	<5	<20	621	0.22	<10	31	<10	2	105	
45	7R18045	<0.2	6.25	10	525	<5	2.90	<1	2	66	64	1.55	0.74	<10	0.42	357	18	2.88	5	520	22	<5	<20	630	0.23	<10	33	<10	2	66	
54	7R18054	<0.2	6.68	5	655	<5	2.32	<1	2	66	8	1.08	0.81	<10	0.27	168	<1	3.09	4	300	26	<5	<20	579	0.15	<10	14	<10	2	58	
71	7R18071	0.2	6.00	10	530	<5	2.74	<1	2	50	114	1.40	0.76	<10	0.39	283	24	2.83	5	480	22	<5	<20	524	0.20	<10	29	<10	2	62	
80	7R18080	<0.2	6.10	5	535	<5	2.43	3	2	69	100	1.69	1.04	<10	0.41	335	44	2.73	6	500	24	<5	<20	515	0.22	<10	31	<10	2	273	
89	7R18089	0.2	6.21	5	550	<5	2.58	<1	2	53	124	1.49	0.87	<10	0.37	260	37	2.85	5	490	22	<5	<20	519	0.22	<10	33	<10	2	74	
106	7R18106	<0.2	7.11	5	605	<5	2.72	<1	2	66	9	1.43	0.76	<10	0.39	241	46	3.11	5	520	26	<5	<20	671	0.23	<10	31	<10	2	46	
115	7R18115	0.2	7.35	<5	870	20	2.16	<1	1	93	74	1.29	1.63	<10	0.28	229	21	2.78	4	390	28	<5	<20	529	0.15	<10	21	<10	8	49	
124	7R18124	<0.2	7.27	5	640	<5	3.08	<1	2	91	31	1.53	0.79	<10	0.43	268	149	3.04	5	550	24	<5	<20	740	0.23	<10	29	<10	1	54	
<i>Resplit:</i>																															
1	7R18001	1.4	6.10	10	450	105	2.53	<1	2	42	59	1.39	1.00	<10	0.32	346	58	2.03	4	510	30	<5	<20	400	0.20	<10	25	<10	3	58	
36	7R18036	<0.2	6.67	5	510	<5	2.86	<1	3	77	61	1.62	0.81	<10	0.42	329	151	2.88	6	520	24	<5	<20	624	0.23	<10	32	<10	2	113	
71	7R18071	0.3	6.02	10	540	<5	2.62	<1	2	59	114	1.56	0.82	<10	0.41	315	31	2.98	4	520	24	<5	<20	537	0.23	<10	34	<10	2	69	
106	7R18106	<0.2	7.32	5	615	<5	2.68	<1	2	66	11	1.51	0.79	<10	0.42	232	35	3.10	6	520	22	<5	<20	717	0.23	<10	30	<10	2	51	
<i>Standard:</i>																															
STSD - 3		0.5	5.89	25	1370	<5	2.47	1	17	62	49	4.17	1.31	40	1.31	2570	7	1.12	31	1620	60	5	<20	269	0.35	<10	116	<10	33	213	
STSD - 3		0.5	5.91	25	1410	<5	2.42	1	17	63	41	4.16	1.30	40	1.30	2603	7	1.13	32	1640	56	<5	<20	272	0.35	<10	121	<10	33	212	
STSD - 3		0.5	5.93	25	1390	<5	2.54	1	17	63	42	4.22	1.39	40	1.32	2552	6	1.17	32	1680	56	<5	<20	274	0.37	<10	120	<10	30	205	
STSD - 3		0.4	5.90	25	1420	<5	2.52	1	17	63	42	4.22	1.39	40	1.31	2574	6	1.15	32	1670	56	<5	<20	270	0.36	<10	122	<10	29	207	

JJ:jl
dl1d1623
XLS/07


 ECO TECH LABORATORY LTD.
 Jutta Jealouse
 B.C. Certified Assayer

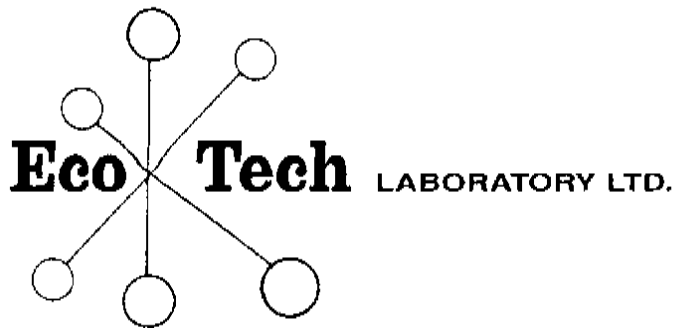

ASSAYING, GEOCHEMISTRY
ANALYTICAL CHEMISTRY
ENVIRONMENTAL TESTING
ISO 9001 Accredited Co.

10041 Dallas Drive, Kamloops, BC V2C 6T4
Phone (250) 573-5700 Fax (250) 573-4557
E-mail: info@ecotechlab.com
www.ecotechlab.com

CERTIFICATE OF ASSAY AK 2007-1510

Pacific Cascade Resources
520 - 700 W. Pender Street
Vancouver, BC
V6C 1G8

18-Oct-07

No. of samples received: 141
Sample Type: Core
Project: Crack Moly
Submitted by: Wesley Raven
Submitted by: Pacific Cascade Resources

ET #.	Tag #	Mo (%)
2	7R17734	0.076
7	7R17739	0.052
20	7R17752	0.064
41	7R17773	0.065
42	7R17774	0.066
45	7R17777	0.214
52	7R17784	0.092
53	7R17785	0.163
62	7R17794	0.138
66	7R17798	0.152
70	7R17802	0.056
72	7R17804	0.055
78	7R17810	0.087
86	7R17818	0.064
89	7R17821	0.052
105	7R17837	0.071
123	7R17855	0.064

QC DATA:

Repeat:

2	7R17734	0.077
42	7R17774	0.065

Standard:

MP2	0.284
MP2	0.281
MP2	0.272
MP2	0.279

JJ/ml
XLS/07

ECO TECH LABORATORY LTD.

Jutta Jealous
B.C. Certified Assayer

ECO TECH LABORATORY LTD.

10041 Dallas Drive
KAMLOOPS, B.C.
V2C 6T4

ICP CERTIFICATE OF ANALYSIS AK 2007- 1510

Pacific Cascade Resources

520 - 700 W. Pender Street
Vancouver, BC
V6C 1G8

Phone: 250-573-5700

Fax : 250-573-4557

No. of samples received: 141

Sample Type: Core

Project: Crack Moly

Submitted by: Wesley Raven

Values in ppm unless otherwise reported

Et #.	Tag #	Ag	Al%	As	Ba	Bi	Ca%	Cd	Co	Cr	Cu	Fe%	K%	La	Mg%	Mn	Mo	Na%	Ni	P	Pb	Sb	Sn	Sr	Ti%	U	V	W	Y	Zn
1	7R17733	0.2	5.37	5	600	<5	2.09	<1	2	103	16	1.20	0.82	<10	0.28	259	118	2.62	6	420	24	<5	<20	578	0.18	<10	22	<10	3	47
2	7R17734	<0.2	5.78	10	630	<5	2.25	<1	<1	141	43	1.25	0.82	<10	0.26	248	759	2.58	6	410	24	<5	<20	590	0.17	<10	21	<10	3	49
3	7R17735	0.2	5.94	10	590	<5	1.88	<1	2	180	24	1.23	1.00	<10	0.21	255	35	2.63	6	410	26	<5	<20	537	0.17	<10	20	<10	2	51
4	7R17736	<0.2	5.56	5	585	<5	2.43	<1	1	115	16	1.15	0.81	<10	0.27	246	236	2.81	5	360	22	<5	<20	600	0.17	<10	20	<10	3	41
5	7R17737	<0.2	5.86	5	485	<5	2.05	<1	1	152	49	1.13	0.94	<10	0.18	237	244	2.66	5	390	24	<5	<20	533	0.17	<10	21	<10	3	48
6	7R17738	0.8	5.91	45	495	<5	1.43	1	3	152	734	1.38	1.01	<10	0.17	192	81	2.35	6	360	26	<5	<20	429	0.15	<10	18	<10	3	67
7	7R17739	<0.2	5.78	10	560	<5	2.03	<1	<1	176	53	1.28	0.82	<10	0.29	290	513	2.50	5	400	24	<5	<20	592	0.16	<10	20	<10	3	49
8	7R17740	0.2	5.70	15	525	<5	1.90	<1	2	127	57	1.41	0.95	<10	0.27	270	123	2.61	6	400	24	<5	<20	528	0.16	<10	20	<10	3	51
9	7R17741	<0.2	5.85	15	1425	10	0.42	<1	<1	73	59	0.45	2.93	10	0.03	68	27	2.16	3	130	34	<5	<20	172	0.02	<10	<1	<10	11	35
10	7R17742	0.2	5.88	60	1375	5	0.47	<1	<1	83	136	0.82	2.85	10	0.05	76	59	1.64	4	130	32	<5	<20	162	0.02	<10	2	<10	13	35
11	7R17743	<0.2	5.39	10	565	<5	1.73	<1	2	153	70	1.36	0.89	<10	0.31	268	47	2.73	5	380	18	<5	<20	556	0.17	<10	20	<10	2	57
12	7R17744	<0.2	5.66	<5	600	<5	2.08	<1	2	115	46	1.34	1.02	<10	0.32	261	24	2.95	6	390	20	<5	<20	550	0.17	<10	23	<10	3	101
13	7R17745	<0.2	5.74	<5	585	<5	2.09	<1	1	113	22	1.19	0.86	<10	0.28	242	18	2.92	4	360	20	<5	<20	603	0.16	<10	20	<10	2	95
14	7R17746	<0.2	6.01	15	600	<5	2.22	<1	2	117	52	1.27	0.98	<10	0.30	251	41	2.89	5	370	24	<5	<20	558	0.16	<10	20	<10	3	68
15	7R17747	1.2	5.90	<5	635	<5	2.32	<1	2	133	529	1.25	1.03	<10	0.31	249	22	3.08	5	370	22	<5	<20	597	0.16	<10	20	<10	3	119
16	7R17748	<0.2	6.01	10	590	<5	2.26	5	1	109	31	1.26	0.97	<10	0.31	242	242	2.93	6	390	24	<5	<20	569	0.16	<10	19	<10	2	157
17	7R17749	<0.2	5.52	<5	600	<5	2.28	<1	1	125	35	1.44	1.11	<10	0.32	257	378	2.84	5	400	20	<5	<20	523	0.18	<10	22	<10	2	112
18	7R17750	<0.2	5.35	10	505	<5	2.26	<1	1	105	34	1.26	0.98	<10	0.28	287	151	2.59	5	440	20	<5	<20	496	0.16	<10	20	<10	3	49
19	7R17751	<0.2	7.28	50	585	<5	2.61	<1	1	127	17	1.24	0.95	<10	0.27	235	230	2.81	5	360	18	<5	<20	525	0.16	<10	19	<10	3	50
20	7R17752	<0.2	7.24	10	825	<5	1.96	<1	5	21	130	2.67	3.14	30	0.54	595	639	1.81	16	820	20	<5	<20	310	0.23	<10	42	<10	14	85
21	7R17753	<0.2	6.73	<5	575	<5	2.60	<1	1	96	13	1.16	0.90	<10	0.30	216	138	2.78	4	340	18	<5	<20	553	0.16	<10	19	<10	2	46
22	7R17754	0.2	6.66	<5	485	<5	2.62	<1	1	126	14	1.13	0.97	<10	0.27	222	65	2.81	4	350	20	<5	<20	519	0.15	<10	19	<10	2	44
23	7R17755	<0.2	6.48	<5	500	<5	2.43	<1	<1	103	9	1.16	0.91	<10	0.30	234	284	2.84	5	370	18	<5	<20	538	0.15	<10	20	<10	3	35
24	7R17756	<0.2	6.98	<5	530	<5	2.64	<1	1	143	13	1.22	0.88	<10	0.26	213	36	2.99	5	360	22	<5	<20	540	0.16	<10	20	<10	2	37
25	7R17757	0.4	6.65	<5	530	<5	2.55	<1	1	106	44	1.25	1.04	<10	0.27	259	95	2.87	5	360	20	<5	<20	523	0.16	<10	20	<10	2	44

Et #.	Tag #	Ag	Al%	As	Ba	Bi	Ca%	Cd	Co	Cr	Cu	Fe%	K%	La	Mg%	Mn	Mo	Na%	Ni	P	Pb	Sb	Sn	Sr	Ti%	U	V	W	Y	Zn
26	7R17758	<0.2	6.48	20	545	<5	2.60	<1	2	112	42	1.30	1.09	<10	0.26	270	34	2.92	5	360	22	<5	<20	527	0.15	<10	19	<10	3	47
27	7R17759	<0.2	6.25	100	885	<5	0.97	<1	<1	79	65	0.66	2.18	10	0.06	102	205	1.95	3	140	30	<5	<20	198	0.02	<10	<1	<10	9	41
28	7R17760	0.2	5.60	5	605	<5	2.36	<1	2	103	16	1.22	0.91	<10	0.30	237	68	3.02	5	350	20	<5	<20	592	0.16	<10	20	<10	3	43
29	7R17761	0.2	6.09	5	585	<5	2.45	<1	1	136	50	1.27	0.89	<10	0.31	282	191	2.93	6	430	20	<5	<20	593	0.16	<10	18	<10	3	41
30	7R17762	0.2	6.14	5	470	<5	2.02	<1	1	126	87	1.71	1.71	<10	0.24	274	270	2.44	5	480	24	<5	<20	453	0.13	<10	17	<10	3	47
31	7R17763	<0.2	5.68	10	560	<5	2.23	2	2	124	47	1.68	1.04	<10	0.32	375	94	2.83	5	460	20	<5	<20	500	0.18	<10	30	<10	5	98
32	7R17764	<0.2	5.55	5	565	<5	2.21	<1	1	110	20	1.75	1.00	<10	0.33	346	195	2.69	6	460	22	<5	<20	473	0.19	<10	30	<10	5	64
33	7R17765	<0.2	6.05	10	1235	<5	1.16	<1	<1	83	42	0.70	2.78	10	0.11	155	82	2.15	4	180	30	<5	<20	255	0.05	<10	7	<10	10	47
34	7R17766	<0.2	6.07	15	1230	<5	1.08	<1	<1	99	47	0.81	2.72	10	0.10	164	118	2.12	3	190	30	<5	<20	240	0.05	<10	7	<10	10	47
35	7R17767	<0.2	6.54	5	720	<5	2.60	<1	3	135	17	2.16	1.12	<10	0.52	392	186	2.72	8	570	22	<5	<20	522	0.27	<10	45	<10	5	65
36	7R17768	<0.2	6.35	5	680	<5	2.39	<1	3	116	44	2.23	1.18	<10	0.49	426	256	2.95	7	610	22	<5	<20	516	0.26	<10	43	<10	4	70
37	7R17769	<0.2	5.93	5	1390	<5	0.73	<1	<1	65	48	0.64	3.02	10	0.06	117	43	2.40	3	140	30	<5	<20	201	0.03	<10	2	<10	12	62
38	7R17770	<0.2	5.65	5	565	<5	2.12	<1	1	166	85	1.44	1.06	<10	0.31	313	67	2.98	6	380	20	<5	<20	534	0.16	<10	22	<10	3	42
39	7R17771	<0.2	6.67	5	515	<5	2.43	<1	2	124	18	1.32	0.77	<10	0.33	293	57	2.85	6	400	22	<5	<20	613	0.17	<10	21	<10	2	42
40	7R17772	<0.2	5.95	5	535	<5	2.24	<1	<1	132	32	1.31	0.83	<10	0.31	315	475	2.99	5	430	22	<5	<20	590	0.16	<10	21	<10	3	44
41	7R17773	0.2	6.43	5	845	<5	1.68	<1	5	22	129	2.66	3.24	30	0.55	595	637	1.70	16	840	22	<5	<20	312	0.23	<10	43	<10	15	83
42	7R17774	<0.2	6.03	5	525	<5	2.13	<1	<1	124	30	1.25	0.79	<10	0.30	294	634	2.71	5	470	22	<5	<20	581	0.15	<10	19	<10	3	46
43	7R17775	<0.2	6.29	10	625	<5	1.91	<1	2	162	46	1.54	1.21	<10	0.33	292	136	2.76	6	400	38	<5	<20	554	0.16	<10	21	<10	3	52
44	7R17776	<0.2	5.90	10	515	<5	2.12	<1	1	106	67	1.46	1.05	<10	0.31	320	184	3.11	5	460	22	<5	<20	494	0.18	<10	23	<10	3	49
45	7R17777	<0.2	5.34	15	475	<5	1.85	<1	<1	169	98	1.37	1.01	<10	0.24	269	2077	2.45	5	750	20	<5	<20	470	0.13	<10	17	<10	5	33
46	7R17778	<0.2	5.40	5	665	<5	1.75	<1	<1	118	30	1.14	1.29	<10	0.23	266	338	2.82	4	420	20	<5	<20	485	0.14	<10	17	<10	4	46
47	7R17779	<0.2	5.83	25	585	<5	1.60	<1	1	144	43	1.39	1.01	<10	0.28	290	250	2.96	5	450	22	<5	<20	532	0.17	<10	21	<10	3	57
48	7R17780	<0.2	5.61	10	495	<5	2.11	<1	1	161	32	1.45	0.85	<10	0.28	310	190	2.86	5	400	20	<5	<20	545	0.16	<10	21	<10	2	45
49	7R17781	<0.2	5.47	5	600	<5	2.24	<1	2	160	11	1.30	0.95	<10	0.28	258	19	3.08	6	380	18	<5	<20	556	0.17	<10	20	<10	2	44
50	7R17782	<0.2	5.60	5	550	<5	2.26	<1	1	167	22	1.40	0.90	<10	0.29	313	202	2.90	5	390	22	<5	<20	543	0.17	<10	20	<10	2	45
51	7R17783	<0.2	5.08	5	605	<5	1.89	<1	1	151	37	1.33	1.10	<10	0.25	259	168	2.91	6	330	18	<5	<20	496	0.14	<10	18	<10	3	41
52	7R17784	<0.2	5.24	5	500	<5	1.97	<1	<1	148	31	1.50	0.99	<10	0.28	293	895	3.04	6	510	20	<5	<20	468	0.17	<10	22	<10	3	40
53	7R17785	<0.2	5.08	10	695	<5	0.88	<1	<1	129	83	1.10	1.94	<10	0.11	185	1544	2.96	4	270	22	<5	<20	270	0.08	<10	10	<10	3	26
54	7R17786	<0.2	5.54	5	615	<5	1.51	<1	<1	164	41	1.33	1.31	<10	0.21	250	454	2.87	6	340	22	<5	<20	449	0.14	<10	17	<10	3	37
55	7R17787	<0.2	5.76	<5	780	<5	1.78	<1	<1	121	30	1.07	1.79	<10	0.20	239	140	2.47	5	290	22	<5	<20	408	0.11	<10	15	<10	4	33
56	7R17788	<0.2	5.46	5	575	<5	2.11	<1	1	152	24	1.25	0.93	<10	0.27	281	54	2.88	5	350	20	<5	<20	552	0.15	<10	19	<10	3	41
57	7R17789	<0.2	5.48	10	515	<5	2.13	<1	2	147	41	1.47	0.87	<10	0.29	337	74	2.83	6	410	18	<5	<20	541	0.16	<10	19	<10	2	90
58	7R17790	<0.2	5.23	10	465	<5	2.17	<1	1	169	50	1.39	0.93	<10	0.27	334	215	2.80	6	380	20	<5	<20	455	0.16	<10	21	<10	2	46
59	7R17791	0.4	5.87	15	1315	<5	0.77	<1	<1	78	32	0.68	2.96	10	0.05	138	107	2.45	3	130	30	<5	<20	185	0.02	<10	<1	<10	9	33
60	7R17792	1.2	4.92	10	1260	<5	0.74	<1	<1	94	388	0.74	2.92	10	0.05	148	31	2.41	3	120	26	<5	<20	155	0.02	<10	1	<10	8	52
61	7R17793	0.2	5.35	5	1220	<5	0.84	<1	<1	85	38	0.77	2.89	10	0.07	150	244	2.32	3	160	26	<5	<20	177	0.03	<10	3	<10	9	31
62	7R17794	<0.2	5.06	10	1090	10	0.65	<1	<1	102	59	0.72	2.71	10	0.03	127	1277	2.01	3	140	24	<5	<20	142	0.02	<10	2	<10	9	53
63	7R17795	<0.2	5.31	10	1245	10	0.62	<1	<1	101	70	0.73	2.99	10	0.06	107	341	1.96	3	110	28	<5	<20	146	0.02	<10	3	<10	9	42
64	7R17796	0.2	5.61	10	1250	<5	0.69	<1	<1	90	53	0.68	2.99	10	0.04	108	261	2.23	4	120	26	<5	<20	153	0.02	<10	1	<10	9	41
65	7R17797	<0.2	6.89	5	795	<5	1.98	<1	2	124	13	1.48	2.03	<10	0.34	317	11	2.56	5	460	26	<5	<20	469	0.19	<10	27	<10	2	53

Et #.	Tag #	Ag	Al%	~As	Ba	Bi	Ca%	Cd	Co	Cr	Cu	Fe%	K%	La	Mg%	Mn	Mo	Na%	Ni	P	Pb	Sb	Sn	Sr	Ti%	U	V	W	Y	Zn
66	7R17798	0.2	4.85	5	1240	15	0.67	<1	<1	85	103	0.68	3.08	<10	0.02	111	1425	2.16	3	120	32	<5	<20	138	0.02	<10	3	<10	10	26
67	7R17799	0.2	4.96	<5	1140	<5	0.73	<1	<1	103	56	0.63	2.85	<10	0.04	137	474	2.24	3	120	26	<5	<20	126	0.02	<10	2	<10	9	46
68	7R17800	<0.2	5.15	<5	1165	<5	0.61	<1	<1	107	58	0.68	2.97	<10	0.03	122	201	2.20	4	140	26	<5	<20	128	0.02	<10	2	<10	8	52
69	7R17801	<0.2	4.44	<5	960	5	0.67	<1	<1	120	40	0.65	2.28	<10	0.03	125	433	1.85	3	110	24	<5	<20	129	0.02	<10	2	<10	8	26
70	7R17802	0.4	5.04	5	1195	5	0.68	<1	<1	87	62	0.72	2.84	<10	0.04	124	535	2.25	3	120	28	<5	<20	140	0.02	<10	2	<10	9	44
71	7R17803	<0.2	4.67	<5	1215	<5	0.69	<1	<1	71	42	0.65	2.94	<10	0.03	135	473	2.44	3	120	26	<5	<20	119	0.02	<10	3	<10	8	23
72	7R17804	<0.2	4.62	<5	1195	<5	0.66	<1	<1	82	65	0.70	2.93	<10	0.02	112	513	2.30	2	110	34	<5	<20	123	0.02	<10	3	<10	8	24
73	7R17805	<0.2	4.49	5	1220	<5	0.75	<1	<1	78	49	0.67	2.99	<10	0.04	120	112	2.30	3	110	22	<5	<20	132	0.02	<10	2	<10	8	30
74	7R17806	<0.2	5.09	<5	1240	<5	0.78	<1	1	81	38	0.68	2.94	<10	0.03	110	31	2.64	3	120	26	<5	<20	131	0.02	<10	3	<10	8	35
75	7R17807	<0.2	4.46	5	1220	<5	0.78	<1	<1	78	48	0.63	2.89	<10	0.04	108	81	2.26	3	110	24	<5	<20	142	0.02	<10	2	<10	8	25
76	7R17808	0.4	4.85	<5	980	<5	1.30	<1	<1	96	37	0.79	2.16	<10	0.13	184	24	2.37	3	200	24	<5	<20	291	0.07	<10	9	<10	7	32
77	7R17809	<0.2	5.43	<5	425	<5	2.28	<1	1	136	19	1.33	0.78	<10	0.23	335	20	3.00	6	400	20	<5	<20	471	0.15	<10	20	<10	3	45
78	7R17810	1.2	5.22	15	475	<5	2.29	1	2	190	989	2.23	0.86	<10	0.25	341	861	2.97	7	410	22	<5	<20	479	0.16	<10	22	<10	2	112
79	7R17811	0.6	5.04	5	460	<5	2.29	<1	1	138	65	1.35	0.91	<10	0.26	319	181	2.82	5	340	18	<5	<20	474	0.15	<10	21	<10	3	38
80	7R17812	<0.2	5.80	<5	445	<5	2.31	<1	1	128	53	1.46	0.85	<10	0.25	248	29	2.95	5	350	22	<5	<20	513	0.15	<10	18	<10	2	37
81	7R17813	<0.2	5.20	5	1165	<5	0.66	<1	<1	82	40	0.44	3.48	10	0.04	70	126	1.66	2	130	30	<5	<20	153	0.02	<10	1	<10	9	12
82	7R17814	0.4	6.01	5	1430	<5	0.62	<1	<1	84	60	0.55	4.05	20	0.04	56	344	1.80	3	130	36	<5	<20	168	0.02	<10	3	<10	8	9
83	7R17815	<0.2	5.85	5	1440	<5	0.59	<1	<1	113	37	0.59	4.03	20	0.05	69	13	1.81	3	140	34	<5	<20	172	0.02	<10	3	<10	9	12
84	7R17816	<0.2	5.59	<5	1625	10	0.74	<1	<1	133	46	0.64	4.13	20	0.05	80	44	1.99	5	140	36	<5	<20	169	0.03	<10	3	<10	9	16
85	7R17817	<0.2	5.54	5	1440	5	0.56	<1	<1	100	52	0.56	3.62	20	0.04	57	98	1.86	3	130	32	<5	<20	166	0.02	<10	3	<10	7	15
86	7R17818	<0.2	6.37	10	850	<5	1.71	<1	5	20	132	2.66	3.17	30	0.55	599	623	1.69	16	840	24	<5	<20	300	0.25	<10	46	<10	15	90
87	7R17819	<0.2	5.79	5	1310	10	0.59	3	<1	100	134	0.72	3.26	10	0.05	84	56	2.03	3	140	32	<5	<20	151	0.02	<10	3	<10	8	191
88	7R17820	<0.2	5.42	5	1455	<5	0.59	<1	<1	98	38	0.46	3.47	20	0.03	55	37	1.82	3	120	30	<5	<20	171	0.02	<10	2	<10	7	16
89	7R17821	<0.2	5.73	30	1475	<5	0.67	<1	<1	110	48	0.58	3.87	20	0.03	84	548	1.91	4	140	34	<5	<20	166	0.02	<10	3	<10	6	15
90	7R17822	<0.2	5.27	5	1400	10	0.67	2	<1	151	65	0.60	3.69	20	0.04	79	11	1.69	4	120	32	<5	<20	152	0.02	<10	2	<10	7	106
91	7R17823	<0.2	5.89	10	1690	5	0.69	<1	<1	140	110	0.73	4.19	20	0.04	92	38	1.89	5	150	34	<5	<20	200	0.02	<10	3	<10	8	20
92	7R17824	<0.2	5.03	<5	1755	<5	0.72	3	<1	106	54	0.55	3.74	20	0.04	80	39	1.46	3	120	28	<5	<20	178	0.02	<10	2	<10	9	156
93	7R17825	<0.2	4.80	<5	1215	5	0.55	<1	<1	101	75	0.69	3.34	10	0.03	86	38	2.05	3	120	28	<5	<20	96	0.02	<10	1	<10	9	16
94	7R17826	<0.2	5.29	10	1230	5	0.62	<1	<1	138	86	0.82	3.33	10	0.03	94	126	2.16	4	120	30	<5	<20	99	0.02	<10	2	<10	9	12
95	7R17827	<0.2	5.51	5	1305	<5	0.57	<1	<1	124	55	0.70	3.60	10	0.03	90	39	2.00	4	130	34	<5	<20	107	0.02	<10	2	<10	10	19
96	7R17828	<0.2	4.65	5	1240	<5	0.58	<1	<1	136	59	0.72	3.32	10	0.03	88	134	2.08	4	130	28	<5	<20	95	0.02	<10	1	<10	9	12
97	7R17829	0.2	4.71	5	1175	<5	0.61	<1	<1	113	77	0.73	3.29	10	0.04	100	44	2.10	3	160	30	<5	<20	100	0.03	<10	<1	<10	9	17
98	7R17830	0.2	5.62	5	1455	5	0.74	<1	<1	92	85	0.58	3.33	20	0.04	63	17	1.94	3	140	30	<5	<20	209	0.02	<10	3	<10	7	22
99	7R17831	0.2	5.40	5	1505	<5	0.55	<1	<1	75	28	0.47	3.40	20	0.04	71	12	1.98	3	130	34	<5	<20	184	0.02	<10	2	<10	8	23
100	7R17832	0.2	5.44	5	1535	<5	0.55	<1	<1	88	49	0.51	3.51	20	0.04	73	28	1.62	3	130	32	<5	<20	194	0.02	<10	3	<10	8	18
101	7R17833	<0.2	5.94	15	1680	5	0.66	<1	<1	111	50	0.55	4.40	20	0.04	67	76	1.42	4	130	34	<5	<20	199	0.02	<10	3	<10	6	26
102	7R17834	0.4	5.60	10	1345	<5	0.60	<1	<1	90	103	0.73	3.49	10	0.04	71	30	1.79	4	140	32	<5	<20	176	0.02	<10	4	<10	8	15
103	7R17835	<0.2	5.72	5	1185	<5	0.68	<1	<1	107	32	0.66	3.16	10	0.06	111	25	2.09	4	140	28	<5	<20	163	0.03	<10	5	<10	8	44
104	7R17836	<0.2	5.20	5	840	<5	1.24	<1	<1	107	36	1.04	2.25	10	0.14	227	227	2.44	5	260	28	<5	<20	283	0.09	<10	14	<10	5	40
105	7R17837	<0.2	4.56	5	1215	<5	0.53	<1	<1	79	58	0.63	3.25	10	0.03	81	711	1.82	3	120	28	<5	<20	100	0.02	<10	2	<10	8	15

Et #.	Tag #	Ag	Al%	As	Ba	Bi	Ca%	Cd	Co	Cr	Cu	Fe%	K%	La	Mg%	Mn	Mo	Na%	Ni	P	Pb	Sb	Sn	Sr	Ti%	U	V	W	Y	Zn
106	7R17838	0.2	6.26	5	1055	<5	1.39	<1	<1	88	31	0.99	2.10	10	0.15	259	18	2.28	3	260	34	<5	<20	329	0.09	<10	6	<10	8	47
107	7R17839	<0.2	6.55	5	855	<5	1.94	<1	<1	124	32	1.07	1.64	10	0.20	294	21	2.50	5	330	32	<5	<20	445	0.11	<10	12	<10	8	45
108	7R17840	<0.2	6.59	5	1210	<5	1.22	<1	<1	147	53	0.99	2.55	10	0.11	210	80	2.02	4	260	40	<5	<20	238	0.07	<10	4	<10	11	39
109	7R17841	<0.2	6.59	5	1490	<5	0.87	<1	<1	112	88	0.85	2.96	10	0.05	138	10	2.03	3	180	42	<5	<20	159	0.03	<10	<1	<10	11	49
110	7R17842	0.2	5.86	5	1525	<5	0.78	<1	<1	128	65	0.80	2.95	10	0.06	132	41	1.86	4	180	38	<5	<20	165	0.03	<10	<1	<10	11	40
111	7R17843	0.2	5.82	10	1280	<5	0.86	<1	<1	166	85	0.96	2.91	10	0.09	144	15	1.88	4	220	36	<5	<20	197	0.05	<10	5	<10	10	31
112	7R17844	<0.2	6.43	5	1080	<5	1.34	<1	<1	156	66	1.11	2.43	10	0.13	243	33	2.34	4	240	34	<5	<20	301	0.07	<10	5	<10	9	45
113	7R17845	<0.2	6.49	5	1525	<5	0.69	<1	<1	92	30	0.78	3.44	10	0.05	179	23	2.07	3	150	38	<5	<20	148	0.03	<10	<1	<10	10	33
114	7R17846	0.2	6.77	<5	1080	<5	1.28	<1	<1	87	39	0.97	2.41	10	0.14	204	56	2.24	3	240	32	<5	<20	282	0.08	<10	9	<10	9	42
115	7R17847	0.2	6.41	10	1465	<5	0.80	<1	<1	112	62	0.74	3.12	20	0.07	127	59	1.85	3	170	34	<5	<20	193	0.03	<10	<1	<10	13	34
116	7R17848	0.2	6.80	5	695	<5	2.25	<1	2	166	54	1.53	1.21	<10	0.29	378	27	2.70	6	450	26	<5	<20	538	0.17	<10	17	<10	5	94
117	7R17849	<0.2	6.44	5	830	<5	1.67	5	1	151	145	1.65	1.74	<10	0.28	287	9	2.14	6	400	26	<5	<20	434	0.15	<10	20	<10	7	336
118	7R17850	<0.2	5.95	<5	670	<5	1.55	4	2	173	168	1.79	1.59	<10	0.25	322	9	2.08	5	400	24	<5	<20	384	0.13	<10	14	<10	6	308
119	7R17851	0.2	5.96	5	615	<5	1.73	<1	1	141	78	1.49	1.35	<10	0.25	254	4	2.31	5	390	24	<5	<20	424	0.14	<10	15	<10	6	55
120	7R17852	<0.2	6.20	5	805	<5	1.58	<1	1	154	62	1.34	1.73	<10	0.23	242	12	2.47	4	360	26	<5	<20	408	0.12	<10	13	<10	6	46
121	7R17853	<0.2	6.55	<5	710	<5	1.97	<1	<1	181	52	1.43	1.62	<10	0.24	311	73	2.43	7	400	26	<5	<20	412	0.14	<10	16	<10	7	46
122	7R17854	<0.2	6.40	10	610	<5	2.57	<1	2	143	31	1.69	1.07	<10	0.37	381	52	2.78	6	530	24	<5	<20	546	0.22	<10	31	<10	5	69
123	7R17855	0.2	6.62	10	840	<5	1.69	<1	5	20	108	2.63	2.96	30	0.55	613	645	1.67	16	860	24	<5	<20	319	0.25	<10	42	<10	15	96
124	7R17856	<0.2	6.13	5	1250	<5	1.01	<1	<1	169	129	1.39	2.78	10	0.15	174	24	1.93	5	270	30	<5	<20	246	0.08	<10	8	<10	10	44
125	7R17857	0.2	6.55	5	1050	<5	1.40	<1	<1	124	81	1.30	2.34	10	0.20	264	71	2.49	3	310	30	<5	<20	329	0.10	<10	11	<10	10	45
126	7R17858	<0.2	6.91	<5	885	<5	1.76	<1	<1	121	59	1.43	1.90	<10	0.23	280	7	2.60	4	400	30	<5	<20	401	0.13	<10	13	<10	8	56
127	7R17859	<0.2	6.25	<5	1140	<5	1.04	<1	<1	219	136	1.32	2.67	10	0.13	176	210	1.97	5	260	28	<5	<20	255	0.08	<10	10	<10	10	58
128	7R17860	0.4	5.12	5	545	<5	1.00	2	1	130	89	1.63	1.29	<10	0.24	323	6	2.02	5	420	20	<5	<20	328	0.13	<10	18	<10	5	149
129	7R17861	0.4	6.69	10	720	<5	1.64	<1	1	141	126	1.78	1.94	<10	0.28	312	83	2.29	5	420	30	<5	<20	365	0.15	<10	18	<10	6	61
130	7R17862	<0.2	6.34	5	1210	<5	1.10	<1	<1	127	57	1.18	2.37	10	0.17	241	17	2.30	4	250	28	<5	<20	245	0.08	<10	8	<10	9	42
131	7R17863	0.4	6.11	5	1195	<5	0.67	2	<1	157	80	0.95	2.75	10	0.09	186	32	1.84	4	200	32	<5	<20	152	0.04	<10	3	<10	9	132
132	7R17864	0.4	5.93	10	1155	<5	0.80	3	<1	124	78	0.91	2.73	10	0.09	168	42	2.06	4	160	32	<5	<20	158	0.04	<10	3	<10	9	180
133	7R17865	<0.2	6.40	5	1240	<5	0.68	9	<1	123	80	0.76	2.96	20	0.05	90	23	1.64	3	180	38	<5	<20	156	0.03	<10	<1	<10	8	529
134	7R17866	0.2	6.10	5	1320	<5	0.46	12	<1	149	112	0.88	2.96	20	0.07	125	29	1.67	4	190	36	<5	<20	156	0.03	<10	3	<10	8	611
135	7R17867	<0.2	6.41	10	1470	<5	0.62	10	<1	95	117	0.82	3.18	10	0.07	92	34	1.73	2	180	34	<5	<20	165	0.03	<10	<1	<10	6	532
136	7R17868	0.2	6.45	<5	1445	<5	0.77	4	<1	116	51	0.61	3.20	20	0.06	92	12	1.83	3	160	34	<5	<20	193	0.03	<10	2	<10	8	171
137	7R17869	<0.2	6.02	<5	1335	<5	0.61	<1	<1	107	13	0.50	3.02	20	0.06	86	35	2.04	3	170	34	<5	<20	199	0.03	<10	3	<10	7	21
138	7R17870	0.2	5.26	5	1080	<5	0.54	<1	<1	121	25	0.49	2.87	10	0.05	75	5	1.65	4	310	30	<5	<20	156	0.02	<10	2	<10	8	22
139	7R17871	<0.2	5.73	10	1160	<5	0.67	<1	<1	112	105	0.74	3.06	10	0.05	82	131	1.56	3	140	32	<5	<20	147	0.02	<10	<1	<10	8	12
140	7R17872	<0.2	4.65	10	860	<5	0.57	<1	<1	130	81	0.60	2.64	10	0.04	75	51	1.21	4	150	24	<5	<20	114	0.02	<10	2	<10	6	17
141	7R17873	0.6	5.67	10	1140	<5	0.69	<1	<1	93	61	0.63	3.43	20	0.04	75	34	1.82	2	380	32	<5	<20	143	0.02	<10	3	<10	11	10

QC DATA:**Repeat:**

1	7R17733	<0.2	5.42	5	580	<5	1.78	<1	2	102	17	1.22	0.84	<10	0.28	237	114	2.84	5	390	22	<5	<20	552	0.17	<10	23	<10	3	42
10	7R17742	<0.2	5.84	65	1345	10	0.52	<1	<1	85	138	0.81	2.85	10	0.05	80	59	1.61	3	120	28	<5	<20	162	0.02	<10	1	<10	13	35
19	7R17751	0.2	7.34	50	560	<5	2.39	<1	1	126	17	1.18	0.94	<10	0.27	243	216	2.71	5	340	20	<5	<20	508	0.15	<10	18	<10	3	51
36	7R17768	<0.2	6.18	5	670	<5	2.41	<1	2	114	44	2.21	1.16	<10	0.50	427	251	2.89	7	600	22	<5	<20	522	0.26	<10	42	<10	4	71


Et #.	Tag #	Ag	Al%	As	Ba	Bi	Ca%	Cd	Co	Cr	Cu	Fe%	K%	La	Mg%	Mn	Mo	Na%	Ni	P	Pb	Sb	Sn	Sr	Ti%	U	V	W	Y	Zn
45	7R17777	<0.2	5.15	15	445	<5	1.97	<1	<1	175	96	1.36	0.99	<10	0.23	267	2013	2.55	5	760	20	<5	<20	438	0.13	<10	17	<10	5	32
54	7R17786	<0.2	5.53	5	610	<5	1.53	<1	<1	158	40	1.27	1.31	<10	0.21	238	450	2.77	5	330	22	<5	<20	431	0.14	<10	17	<10	3	37
71	7R17803	<0.2	4.92	<5	1220	<5	0.71	<1	<1	72	42	0.65	2.93	<10	0.03	130	476	2.35	2	120	26	<5	<20	131	0.02	<10	2	<10	8	25
80	7R17812	0.2	5.37	<5	430	<5	2.30	<1	2	125	53	1.45	0.85	<10	0.25	249	29	2.97	6	340	20	<5	<20	502	0.15	<10	19	<10	3	38
89	7R17821	0.2	5.66	30	1455	<5	0.67	<1	<1	103	45	0.52	3.88	20	0.03	73	52	1.86	4	140	32	<5	<20	169	0.02	<10	3	<10	6	14
106	7R17838	<0.2	6.14	<5	1005	<5	1.27	<1	<1	86	33	0.96	2.27	10	0.14	259	17	2.43	3	240	30	<5	<20	307	0.08	<10	8	<10	9	41
115	7R17847	0.4	7.01	10	1430	<5	0.90	<1	<1	113	62	0.83	3.12	20	0.07	150	66	1.95	4	180	38	<5	<20	186	0.04	<10	2	<10	12	39
124	7R17856	0.2	6.15	10	1205	<5	1.02	<1	<1	154	132	1.41	2.49	10	0.15	206	24	1.93	5	270	28	<5	<20	236	0.08	<10	7	<10	10	40
141	7R17873	0.4	5.98	10	1155	<5	0.76	<1	<1	91	61	0.65	3.49	20	0.05	84	36	1.68	3	400	30	<5	<20	151	0.02	<10	2	<10	11	12

Resplit:

1	7R17733	<0.2	5.79	10	610	<5	2.08	<1	1	117	20	1.24	0.91	<10	0.28	243	118	2.82	5	390	22	<5	<20	581	0.16	<10	21	<10	3	42
36	7R17768	<0.2	5.84	5	660	<5	2.42	<1	2	116	50	2.28	1.18	<10	0.49	443	271	2.85	7	610	22	<5	<20	491	0.27	<10	47	<10	5	71
71	7R17803	<0.2	4.79	5	1250	<5	0.68	<1	<1	69	40	0.64	2.93	<10	0.03	128	497	2.34	2	130	28	<5	<20	113	0.02	<10	3	<10	8	22
106	7R17838	<0.2	6.22	5	1010	<5	1.28	<1	<1	100	34	1.01	2.27	10	0.15	247	17	2.18	3	240	30	<5	<20	307	0.08	<10	6	<10	8	41
141	7R17873	0.4	6.22	10	1205	<5	0.70	<1	<1	101	66	0.72	3.74	20	0.04	69	33	1.74	4	390	36	<5	<20	152	0.02	<10	2	<10	9	13


Standard:

STSD3		0.5	5.40	20	1320	<5	2.37	<1	15	59	41	4.03	1.34	40	1.22	2409	6	1.10	28	1530	50	<5	<20	247	0.30	<10	113	<10	31	201
STSD3		0.4	5.50	25	1380	<5	2.38	<1	16	62	41	4.05	1.39	40	1.24	2466	6	1.15	29	1550	52	<5	<20	249	0.33	<10	120	<10	32	209
STSD3		0.4	5.88	25	1405	<5	2.48	<1	17	62	42	4.21	1.39	40	1.29	2551	6	1.16	31	1650	56	<5	<20	264	0.35	<10	120	<10	32	206
STSD3		0.5	5.65	25	1415	<5	2.49	<1	17	60	37	4.21	1.31	40	1.30	2606	2	1.09	31	1620	54	<5	<20	254	0.34	<10	112	<10	34	213
STSD3		0.4	5.89	25	1410	<5	2.47	<1	17	61	42	4.18	1.39	30	1.29	2533	7	1.13	31	1660	56	<5	<20	263	0.35	<10	117	<10	32	207

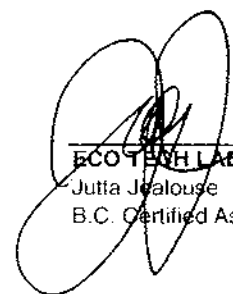

ECO TECH LABORATORY LTD.
 Julia Jalouse
 B.C. Certified Assayer

JJ:nl
 dl:015:0aS:01510bS
 XLS/07

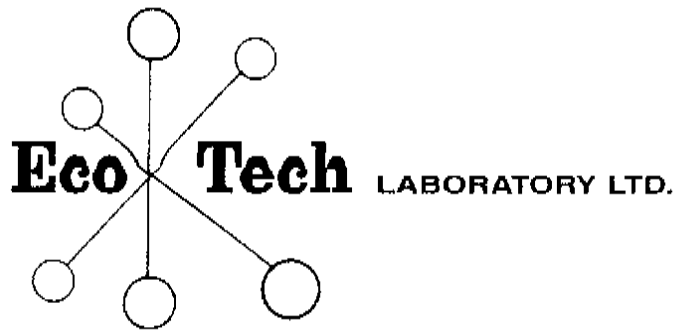

ASSAYING, GEOCHEMISTRY
ANALYTICAL CHEMISTRY
ENVIRONMENTAL TESTING
ISO 9001 Accredited Co.

10041 Dallas Drive, Kamloops, BC V2C 6T4
Phone (250) 573-5700 Fax (250) 573-4557
E-mail: info@ecotechlab.com
www.ecotechlab.com

CERTIFICATE OF ASSAY AK 2007-1519

Pacific Cascade Resources
520 - 700 W. Pender Street
Vancouver, BC
V6C 1G8

19-Oct-07

No. of samples received: 127
Sample Type: Core
Project: Crack Moly
Submitted by: Pacific Cascade

ET #.	Tag #	Mo (%)
5	7R17875	0.052
18	7R17888	0.217
20	7R17890	0.065
21	7R17891	0.065
32	7R17902	0.082
36	7R17906	0.055
53	7R17923	0.074
67	7R17937	0.249
76	7R17946	0.050
80	7R17950	0.064
89	7R17959	0.089

QC DATA:


Repeat:

67 7R17937 0.247

Standard:

MP2 0.281
MP2 0.281

JJ/jl
XLS/07

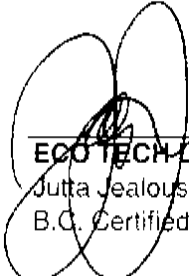
ECO TECH LABORATORY LTD.
Jutta Jealous
B.C. Certified Assayer

ECO TECH LABORATORY LTD.

10041 Dallas Drive
KAMLOOPS, B.C.
V2C 6T4

ICP CERTIFICATE OF ANALYSIS AK 2007- 1519

Pacific Cascade Resources

520 - 700 W. Pender Street
Vancouver, BC
V6C 1G8

Phone: 250-573-5700

Fax : 250-573-4557

No. of samples received: 127

Sample Type: Core

Project: Crack Moly

Submitted by: Pacific Cascade

Values in ppm unless otherwise reported

Et #.	Tag #	Ag	Al%	As	Ba	Bi	Ca%	Cd	Co	Cr	Cu	Fe%	K%	La	Mg%	Mn	Mo	Na%	Ni	P	Pb	Sb	Sn	Sr	Ti%	U	V	W	Y	Zn
1	7R17871A	<0.2	5.93	10	1250	<5	0.43	<1	<1	99	43	0.91	2.18	10	0.06	304	166	2.12	4	160	36	<5	<20	100	0.03	<10	3	<10	10	43
2	7R17872A	0.2	5.11	20	1285	<5	0.57	<1	<1	125	81	0.98	2.58	10	0.05	312	32	2.13	3	140	34	<5	<20	98	0.03	<10	2	<10	10	70
3	7R17873A	0.4	5.13	30	1305	<5	0.54	<1	<1	120	56	0.91	2.62	10	0.06	321	44	2.19	4	140	32	<5	<20	99	0.03	<10	1	<10	9	73
4	7R17874	0.2	5.65	30	1230	<5	0.55	<1	<1	141	191	0.98	1.99	10	0.04	296	485	2.15	4	140	34	<5	<20	98	0.02	<10	1	<10	8	77
5	7R17875	0.4	5.21	35	1265	<5	0.68	<1	<1	125	97	0.93	2.18	10	0.06	224	535	1.94	4	180	34	<5	<20	136	0.03	<10	2	<10	10	78
6	7R17876	0.2	5.39	35	1215	<5	0.50	<1	<1	107	26	0.91	2.27	10	0.07	312	198	2.08	3	160	32	<5	<20	91	0.03	<10	1	<10	10	69
7	7R17877	0.4	5.40	30	1245	<5	0.59	1	<1	125	31	0.91	2.46	10	0.07	306	268	2.23	4	140	32	<5	<20	106	0.03	<10	2	<10	9	72
8	7R17878	<0.2	5.17	5	1265	<5	0.52	<1	<1	92	53	0.87	2.73	10	0.05	258	236	2.17	2	140	32	<5	<20	97	0.03	<10	1	<10	10	56
9	7R17879	0.2	5.99	<5	640	<5	2.00	<1	2	127	144	1.80	1.41	<10	0.36	426	141	2.73	7	540	26	<5	<20	484	0.19	<10	31	<10	4	120
10	7R17880	0.2	7.32	<5	690	<5	2.51	<1	2	138	93	1.73	1.06	<10	0.40	376	59	2.94	6	520	24	<5	<20	583	0.21	<10	32	<10	4	63
11	7R17881	<0.2	7.24	<5	575	<5	2.42	<1	2	136	115	1.74	1.06	<10	0.39	349	67	2.81	6	530	24	<5	<20	564	0.21	<10	33	<10	3	62
12	7R17882	<0.2	7.43	<5	555	<5	2.37	<1	2	170	33	1.59	0.95	<10	0.37	361	219	2.65	7	520	24	<5	<20	576	0.19	<10	28	<10	3	65
13	7R17883	0.4	7.42	<5	645	<5	2.61	<1	2	118	55	1.60	1.15	<10	0.37	361	116	2.95	6	650	22	<5	<20	586	0.20	<10	29	<10	5	65
14	7R17884	0.4	6.46	<5	625	<5	2.48	<1	2	105	187	1.62	1.07	<10	0.41	326	114	2.78	5	530	24	<5	<20	587	0.21	<10	35	<10	3	63
15	7R17885	0.2	5.90	<5	540	<5	2.38	<1	1	133	36	1.67	0.91	<10	0.38	380	439	2.85	6	710	22	<5	<20	580	0.20	<10	29	<10	4	59
16	7R17886	0.4	5.87	<5	565	<5	2.44	<1	2	103	20	1.60	0.90	<10	0.43	368	56	2.92	7	570	22	<5	<20	612	0.21	<10	35	<10	3	56
17	7R17887	0.2	6.06	<5	630	<5	2.42	1	2	120	41	1.65	1.40	<10	0.29	440	68	2.80	6	540	26	<5	<20	417	0.19	<10	30	<10	6	115
18	7R17888	3.2	5.32	<5	460	5	2.16	2	<1	187	1394	1.97	1.37	<10	0.30	381	2081	2.49	5	400	28	<5	<20	433	0.15	<10	23	10	2	113
19	7R17889	<0.2	5.35	5	995	<5	1.03	<1	<1	149	78	1.05	2.22	10	0.13	180	90	2.30	5	250	28	<5	<20	276	0.07	<10	9	<10	11	44
20	7R17890	<0.2	4.97	10	1435	<5	0.53	<1	<1	102	45	0.72	2.73	10	0.04	132	667	2.11	3	140	34	<5	<20	176	0.02	<10	2	<10	11	41
21	7R17891	<0.2	7.33	<5	855	<5	1.49	<1	5	22	132	2.70	2.05	30	0.57	615	648	1.61	17	860	34	<5	<20	333	0.25	<10	43	<10	15	86
22	7R17892	0.4	4.64	<5	540	<5	1.82	<1	2	88	289	1.47	1.17	<10	0.34	316	82	2.76	5	500	24	<5	<20	518	0.18	<10	29	<10	4	65
23	7R17893	0.2	4.87	10	615	<5	1.64	<1	1	122	67	1.64	1.16	<10	0.32	376	155	2.69	5	530	22	<5	<20	506	0.18	<10	25	<10	4	96
24	7R17894	0.2	4.81	150	1160	<5	0.73	2	<1	63	43	0.65	2.45	<10	0.06	115	257	1.97	2	170	34	<5	<20	183	0.03	<10	3	<10	12	64
25	7R17895	0.4	4.82	120	1220	<5	0.33	<1	<1	84	238	0.67	2.19	10	0.05	142	107	1.92	3	150	40	<5	<20	128	0.02	<10	2	<10	16	41

Et #.	Tag #	Ag	Al%	As	Ba	Bi	Ca%	Cd	Co	Cr	Cu	Fe%	K%	La	Mg%	Mn	Mo	Na%	Ni	P	Pb	Sb	Sn	Sr	Ti%	U	V	W	Y	Zn
26	7R17896	0.2	5.70	110	795	<5	1.16	1	1	95	67	1.23	1.41	<10	0.22	211	60	2.06	5	430	30	5	<20	400	0.15	<10	21	<10	8	76
27	7R17897	<0.2	5.28	15	670	<5	1.78	1	2	135	63	1.52	1.17	<10	0.34	278	238	2.76	7	450	22	<5	<20	582	0.18	<10	26	<10	4	90
28	7R17898	<0.2	7.48	<5	710	<5	2.32	<1	2	88	22	1.66	1.24	<10	0.44	391	74	2.89	5	530	26	<5	<20	610	0.21	<10	32	<10	4	87
29	7R17899	<0.2	6.92	<5	720	<5	2.25	2	2	134	76	1.68	1.26	<10	0.40	398	89	2.85	6	520	22	<5	<20	608	0.20	<10	30	10	3	128
30	7R17900	<0.2	6.81	<5	705	<5	2.29	1	2	112	59	1.53	1.25	<10	0.39	341	28	2.80	5	520	24	<5	<20	589	0.19	<10	31	<10	3	101
31	7R17901	<0.2	5.79	10	540	<5	2.14	<1	2	110	25	1.38	1.16	<10	0.28	261	125	2.44	5	470	22	<5	<20	480	0.17	<10	26	<10	2	49
32	7R17902	0.6	6.08	75	550	<5	2.01	1	1	160	221	1.70	1.27	<10	0.29	324	861	2.31	7	480	20	<5	<20	439	0.18	<10	30	<10	3	92
33	7R17903	<0.2	5.83	<5	475	<5	2.17	<1	2	127	140	1.63	1.06	<10	0.34	303	163	2.39	5	590	22	<5	<20	480	0.17	<10	28	<10	3	49
34	7R17904	<0.2	6.23	<5	640	<5	1.88	<1	1	142	46	1.65	1.53	<10	0.30	342	470	2.43	6	420	24	<5	<20	480	0.16	<10	25	<10	4	75
35	7R17905	<0.2	5.89	<5	780	<5	1.51	<1	<1	99	63	1.51	1.78	<10	0.24	345	442	2.19	4	280	24	<5	<20	390	0.12	<10	17	<10	7	76
36	7R17906	0.2	6.61	<5	875	<5	1.11	1	<1	77	250	1.40	2.17	<10	0.20	328	576	2.05	3	310	30	<5	<20	352	0.11	<10	17	<10	8	103
37	7R17907	<0.2	6.68	<5	1430	<5	0.76	1	<1	125	48	0.72	2.68	10	0.09	175	59	1.94	3	170	38	<5	<20	266	0.04	<10	4	30	13	89
38	7R17908	<0.2	6.15	<5	1295	<5	0.79	2	<1	76	29	0.75	2.71	10	0.09	174	141	2.05	3	220	34	<5	<20	267	0.04	<10	4	<10	13	120
39	7R17909	<0.2	7.60	<5	800	<5	2.14	<1	2	129	26	1.73	1.23	<10	0.42	500	1	2.59	6	540	26	<5	<20	621	0.20	<10	32	<10	4	69
40	7R17910	<0.2	6.69	<5	570	<5	2.40	<1	2	132	52	1.85	1.14	<10	0.42	401	304	2.60	7	550	24	<5	<20	582	0.20	<10	32	<10	3	80
41	7R17911	<0.2	6.28	15	565	<5	2.15	<1	2	97	107	1.76	1.14	<10	0.39	354	142	2.70	5	610	22	<5	<20	508	0.20	<10	33	<10	4	65
42	7R17912	<0.2	6.50	<5	565	<5	2.61	<1	2	86	35	1.68	0.96	<10	0.43	384	123	2.79	5	590	22	<5	<20	598	0.22	<10	34	<10	3	65
43	7R17913	0.2	5.91	<5	570	<5	2.41	<1	2	113	222	1.50	0.98	<10	0.39	305	355	2.57	5	500	24	<5	<20	530	0.19	<10	31	<10	3	51
44	7R17914	0.4	6.67	<5	625	<5	2.55	3	2	80	88	1.49	0.94	<10	0.39	337	5	2.86	5	530	20	<5	<20	542	0.20	<10	33	<10	2	135
45	7R17915	0.2	6.01	<5	580	<5	2.56	<1	2	118	97	1.63	0.91	<10	0.39	331	441	2.69	7	520	24	<5	<20	551	0.21	<10	34	<10	3	54
46	7R17916	<0.2	6.68	<5	640	<5	2.39	<1	3	87	155	1.74	1.13	<10	0.40	331	91	2.93	5	550	24	<5	<20	553	0.20	<10	33	30	3	51
47	7R17917	<0.2	6.12	<5	525	<5	2.32	<1	2	169	108	1.61	0.95	<10	0.35	341	100	2.62	7	490	20	<5	<20	501	0.19	<10	31	20	2	58
48	7R17918	0.4	5.99	15	585	<5	2.32	<1	2	124	173	1.56	1.16	<10	0.32	328	114	2.68	6	500	20	<5	<20	464	0.18	<10	30	<10	3	53
49	7R17919	<0.2	5.34	<5	645	<5	2.51	<1	2	81	21	1.46	0.97	<10	0.41	296	6	3.03	6	530	20	<5	<20	584	0.21	<10	34	<10	4	68
50	7R17920	<0.2	5.54	<5	675	<5	2.51	<1	2	136	55	1.67	0.98	<10	0.43	312	40	2.98	7	550	26	<5	<20	572	0.22	<10	35	<10	3	43
51	7R17921	<0.2	5.77	<5	740	<5	2.57	<1	2	141	18	1.44	1.04	<10	0.37	269	2	2.94	6	490	20	<5	<20	542	0.20	<10	32	<10	4	42
52	7R17922	<0.2	4.75	<5	610	<5	2.50	<1	2	57	37	1.49	1.01	<10	0.38	346	21	2.78	5	510	20	<5	<20	491	0.20	<10	35	<10	4	38
53	7R17923	<0.2	4.92	10	605	<5	2.22	<1	<1	121	24	1.55	1.03	<10	0.35	394	796	2.90	5	540	18	<5	<20	485	0.20	<10	31	<10	3	34
54	7R17924	<0.2	6.14	35	655	<5	1.44	<1	2	96	81	1.78	2.04	20	0.24	312	11	2.15	4	400	24	5	<20	242	0.12	<10	6	<10	11	21
55	7R17925	<0.2	5.69	<5	870	<5	1.42	<1	1	110	34	1.66	2.06	20	0.21	283	8	2.54	4	380	22	5	<20	260	0.12	<10	6	<10	12	12
56	7R17926	<0.2	5.42	<5	695	<5	1.45	<1	2	100	47	1.94	1.84	20	0.24	275	4	2.62	4	390	26	10	<20	259	0.14	<10	5	<10	12	20
57	7R17927	<0.2	5.67	10	640	<5	2.31	<1	2	126	46	1.46	1.02	<10	0.39	317	165	2.76	5	500	20	<5	<20	543	0.19	<10	31	<10	3	45
58	7R17928	<0.2	5.40	<5	645	<5	2.39	<1	2	112	47	1.49	1.00	<10	0.36	336	15	2.84	5	480	22	<5	<20	520	0.19	<10	31	<10	3	41
59	7R17929	<0.2	5.06	275	670	<5	2.34	<1	2	157	80	1.66	1.09	<10	0.36	315	2	2.76	8	490	22	<5	<20	472	0.20	<10	33	10	3	46
60	7R17930	<0.2	5.79	265	660	<5	1.69	2	1	127	82	1.72	1.62	<10	0.32	335	406	1.80	7	470	22	5	<20	387	0.17	<10	26	<10	4	66
61	7R17931	<0.2	6.57	260	850	<5	1.71	2	2	75	60	1.73	2.24	20	0.35	347	27	1.60	6	470	26	10	<20	361	0.18	<10	25	<10	7	62
62	7R17932	<0.2	5.90	<5	740	<5	2.37	<1	3	143	109	1.78	1.20	<10	0.39	343	47	2.63	7	530	22	<5	<20	531	0.20	<10	32	<10	3	66
63	7R17933	<0.2	6.21	<5	670	<5	2.56	<1	3	95	69	1.80	0.99	<10	0.44	301	3	2.96	6	540	26	<5	<20	565	0.22	<10	36	<10	3	49
64	7R17934	0.2	6.07	<5	690	<5	2.48	<1	2	66	85	1.54	1.08	<10	0.41	312	104	2.97	6	510	20	<5	<20	552	0.21	<10	33	<10	4	50
65	7R17935	<0.2	6.41	<5	680	<5	2.61	<1	3	75	67	1.57	1.03	<10	0.38	302	46	2.80	4	530	20	<5	<20	533	0.22	<10	35	<10	3	51

Et #.	Tag#	Ag	Al%	As	Ba	Bi	Ca%	Cd	Co	Cr	Cu	Fe%	K%	La	Mg%	Mn	Mo	Na%	Ni	P	Pb	Sb	Sn	Sr	Ti%	U	V	W	Y	Zn
66	7R17936	<0.2	5.52	30	625	<5	2.62	3	2	100	34	1.48	0.93	<10	0.39	299	13	2.94	6	500	20	<5	<20	522	0.21	<10	34	10	3	121
67	7R17937	<0.2	4.55	<5	575	<5	2.12	<1	<1	133	74	1.52	0.96	<10	0.34	365	2521	2.67	5	580	20	<5	<20	490	0.20	<10	32	<10	4	54
68	7R17938	<0.2	6.03	45	580	<5	2.07	<1	2	97	64	1.56	1.10	<10	0.28	360	172	2.65	6	570	20	<5	<20	433	0.21	<10	36	<10	3	65
69	7R17939	<0.2	6.24	10	650	<5	2.57	<1	3	91	34	1.67	1.05	<10	0.39	303	10	2.98	6	590	20	<5	<20	540	0.25	<10	41	<10	3	61
70	7R17940	<0.2	5.75	<5	740	<5	2.32	<1	2	82	41	1.51	1.12	<10	0.31	273	8	2.89	6	510	22	<5	<20	496	0.21	<10	34	<10	4	42
71	7R17941	0.3	6.09	5	715	<5	2.32	<1	2	78	105	1.48	1.40	<10	0.29	328	121	2.76	5	500	20	<5	<20	460	0.20	<10	32	<10	5	46
72	7R17942	0.2	5.76	10	515	<5	2.42	<1	2	78	70	1.44	1.19	<10	0.32	318	95	2.60	5	520	20	<5	<20	431	0.21	<10	33	<10	4	58
73	7R17943	0.2	6.08	<5	605	<5	2.50	<1	3	75	132	1.56	1.05	<10	0.38	304	75	2.85	4	510	20	<5	<20	523	0.21	<10	37	<10	3	43
74	7R17944	0.2	5.22	<5	635	<5	2.59	<1	2	90	49	1.44	0.96	<10	0.39	345	21	2.77	5	530	22	<5	<20	526	0.21	<10	33	<10	4	67
75	7R17945	<0.2	5.87	<5	660	<5	2.69	<1	2	83	60	1.55	0.99	<10	0.38	388	46	2.90	5	530	18	<5	<20	506	0.22	<10	37	<10	3	79
76	7R17946	<0.2	6.05	<5	540	<5	2.50	<1	1	83	38	1.47	0.92	<10	0.38	313	518	2.79	6	490	18	<5	<20	504	0.20	<10	34	<10	3	65
77	7R17947	<0.2	5.95	<5	625	<5	2.58	<1	2	77	32	1.50	1.01	<10	0.40	315	38	3.00	6	500	20	<5	<20	533	0.21	<10	34	<10	3	66
78	7R17948	<0.2	5.67	<5	615	<5	2.63	<1	2	105	78	1.58	0.95	<10	0.39	291	94	2.99	6	520	18	<5	<20	515	0.22	<10	38	<10	3	62
79	7R17949	0.2	5.68	<5	825	<5	2.24	<1	2	78	36	1.32	1.23	<10	0.36	263	35	2.60	4	450	20	<5	<20	510	0.19	<10	30	<10	5	50
80	7R17950	<0.2	7.63	<5	875	<5	1.74	<1	5	19	129	2.82	2.71	30	0.58	627	647	1.79	17	920	32	<5	<20	326	0.27	<10	47	<10	15	90
81	7R17951	<0.2	6.80	<5	905	<5	2.38	<1	2	91	65	1.42	1.55	<10	0.38	301	44	2.83	6	480	24	<5	<20	553	0.20	<10	29	<10	6	82
82	7R17952	<0.2	6.73	<5	735	<5	2.58	<1	2	86	137	1.41	1.18	<10	0.36	267	54	2.93	5	470	20	<5	<20	538	0.19	<10	30	<10	4	60
83	7R17953	0.2	5.70	<5	570	<5	3.04	<1	2	72	43	1.44	1.16	<10	0.36	337	6	2.83	5	500	18	<5	<20	433	0.21	<10	35	<10	4	78
84	7R17954	0.2	4.54	10	685	<5	1.98	<1	2	112	253	1.60	1.18	<10	0.36	405	98	2.72	6	510	22	<5	<20	486	0.20	<10	33	20	4	105
85	7R17955	0.6	5.44	<5	650	<5	2.53	<1	2	92	322	1.60	0.97	<10	0.42	345	198	2.83	5	540	16	<5	<20	507	0.22	<10	34	<10	3	73
86	7R17956	0.6	5.63	<5	615	<5	2.71	<1	2	77	273	1.48	0.89	<10	0.38	328	15	2.90	5	530	20	<5	<20	514	0.22	<10	35	<10	3	70
87	7R17957	0.2	5.72	<5	755	<5	2.51	<1	2	89	136	1.52	1.09	<10	0.35	354	73	2.77	6	500	20	<5	<20	450	0.20	<10	35	<10	4	74
88	7R17958	<0.2	6.26	<5	690	<5	2.61	<1	2	89	86	1.50	0.99	<10	0.37	324	36	2.77	5	530	20	<5	<20	517	0.21	<10	37	<10	3	58
89	7R17959	0.3	4.88	25	495	<5	2.13	<1	1	117	202	1.57	1.13	<10	0.25	297	914	2.00	6	460	18	<5	<20	337	0.16	<10	27	<10	3	59
90	7R17960	<0.2	5.64	<5	620	<5	2.24	<1	2	78	60	1.58	1.09	<10	0.35	317	102	2.81	5	510	18	<5	<20	454	0.21	<10	34	<10	3	97
91	7R17961	0.4	4.65	5	750	<5	2.18	1	2	78	161	1.45	1.16	<10	0.30	335	27	2.75	4	480	18	<5	<20	427	0.19	<10	32	<10	4	95
92	7R17962	0.2	5.17	<5	620	<5	2.53	<1	3	88	111	1.69	0.98	<10	0.36	394	39	2.79	6	530	18	<5	<20	444	0.22	<10	40	<10	2	75
93	7R17963	<0.2	5.49	10	605	<5	2.37	<1	3	75	103	1.43	1.12	<10	0.26	269	45	2.72	5	500	22	<5	<20	394	0.20	<10	35	<10	3	71
94	7R17964	<0.2	5.10	<5	575	<5	2.39	<1	2	70	84	1.58	1.19	<10	0.35	325	17	2.96	5	480	18	<5	<20	421	0.22	<10	36	<10	5	74
95	7R17965	<0.2	5.13	<5	980	<5	1.75	<1	1	83	47	1.27	1.97	<10	0.25	282	3	2.62	4	350	20	<5	<20	335	0.14	<10	25	<10	10	76
96	7R17966	<0.2	6.08	<5	1485	<5	0.87	<1	1	95	27	0.67	2.86	<10	0.07	151	3	2.33	3	170	22	<5	<20	192	0.04	<10	6	<10	15	46
97	7R17967	<0.2	4.69	<5	645	<5	2.20	<1	2	79	62	1.51	1.30	<10	0.32	331	3	2.92	5	450	18	<5	<20	436	0.20	<10	33	<10	6	58
98	7R17968	<0.2	5.67	<5	550	<5	2.56	<1	2	100	63	1.70	1.08	<10	0.36	384	3	3.10	5	520	18	<5	<20	455	0.22	<10	39	<10	5	67
99	7R17969	0.2	6.56	<5	1360	<5	1.31	<1	<1	85	45	0.85	2.51	<10	0.14	179	3	2.51	4	240	24	<5	<20	263	0.08	<10	12	<10	14	55
100	7R17970	<0.2	5.16	<5	1280	<5	0.89	1	1	85	56	0.68	2.42	<10	0.07	131	4	2.14	3	140	26	<5	<20	183	0.03	<10	5	<10	16	94
101	7R17971	<0.2	6.18	<5	975	<5	1.61	<1	1	91	27	1.15	2.10	<10	0.20	281	4	2.53	4	320	22	<5	<20	318	0.11	<10	18	<10	10	79
102	7R17972	<0.2	6.20	<5	1455	<5	1.30	<1	1	92	41	0.82	2.43	<10	0.11	203	9	2.11	4	210	28	<5	<20	274	0.07	<10	11	<10	16	62
103	7R17973	<0.2	5.09	<5	625	<5	2.51	<1	2	78	28	1.42	0.99	<10	0.31	317	<1	2.77	5	470	18	<5	<20	454	0.21	<10	35	<10	4	62
104	7R17974	<0.2	5.23	<5	870	<5	2.17	<1	1	81	31	1.37	1.43	<10	0.30	364	20	2.64	4	420	20	<5	<20	416	0.18	<10	30	<10	5	70
105	7R17975	0.2	6.44	<5	635	<5	2.51	<1	2	87	4	1.17	0.89	<10	0.28	172	1	3.05	5	330	22	<5	<20	567	0.17	<10	16	<10	1	66

Et #.	Tag #	Ag	Al%	As	Ba	Bi	Ca%	Cd	Co	Cr	Cu	Fe%	K%	La	Mg%	Mn	Mo	Na%	Ni	P	Pb	Sb	Sn	Sr	Ti%	U	V	W	Y	Zn
106	7R17976	0.3	5.81	5	790	<5	1.97	<1	2	111	40	1.43	1.24	<10	0.32	370	4	2.44	6	490	30	<5	<20	512	0.20	<10	32	<10	6	74
107	7R17977	<0.2	5.12	5	535	<5	1.79	<1	2	118	90	1.46	0.99	<10	0.34	335	21	2.39	5	480	22	<5	<20	491	0.19	<10	30	<10	4	96
108	7R17978	<0.2	5.70	<5	820	<5	1.86	<1	2	124	58	1.36	1.47	<10	0.27	343	2	2.69	4	460	26	<5	<20	513	0.17	<10	26	20	7	78
109	7R17979	<0.2	5.48	15	695	<5	1.93	<1	2	99	40	1.53	1.27	<10	0.35	400	10	2.68	5	490	22	<5	<20	523	0.21	<10	31	<10	5	94
110	7R17980	0.2	5.68	<5	760	<5	1.92	<1	2	117	109	1.42	1.45	<10	0.30	302	5	2.71	4	410	24	<5	<20	504	0.16	<10	25	<10	8	61
111	7R17981	<0.2	6.65	<5	1060	<5	1.44	1	1	98	147	1.23	2.02	10	0.17	251	12	2.48	5	330	30	<5	<20	334	0.10	<10	15	<10	14	94
112	7R17982	0.2	6.67	<5	1435	<5	1.00	3	1	112	83	0.78	2.14	10	0.07	161	13	2.26	3	160	34	<5	<20	198	0.03	<10	3	<10	16	182
113	7R17983	0.4	6.64	<5	1055	<5	2.24	<1	2	110	49	1.57	1.70	<10	0.31	375	4	2.79	6	430	28	<5	<20	469	0.17	<10	25	<10	8	87
114	7R17984	0.4	6.12	<5	700	<5	2.38	1	2	112	53	1.59	1.29	<10	0.37	397	2	2.71	5	500	24	<5	<20	523	0.20	<10	31	10	6	144
115	7R17985	<0.2	6.19	<5	740	<5	2.37	<1	2	95	28	1.40	1.30	<10	0.35	309	3	2.74	5	470	24	<5	<20	546	0.18	<10	30	<10	6	58
116	7R17986	<0.2	6.77	<5	725	<5	2.63	<1	2	97	65	1.64	1.24	<10	0.37	357	4	2.86	5	530	26	<5	<20	545	0.20	<10	29	<10	5	71
117	7R17987	<0.2	5.73	<5	725	<5	2.37	<1	2	92	72	1.51	1.15	<10	0.36	308	134	2.80	5	490	22	<5	<20	535	0.19	<10	32	<10	5	58
118	7R17988	<0.2	5.89	<5	585	<5	2.38	<1	2	107	105	1.48	1.05	<10	0.34	244	3	2.82	5	490	24	<5	<20	543	0.19	<10	34	<10	4	50
119	7R17989	0.4	6.23	<5	665	<5	2.18	<1	2	82	22	1.48	0.98	<10	0.38	271	<1	3.03	5	530	26	<5	<20	615	0.21	<10	33	<10	4	49
120	7R17990	<0.2	6.38	<5	610	<5	2.56	<1	2	101	46	1.54	0.97	<10	0.38	289	16	2.88	5	490	24	<5	<20	595	0.20	<10	32	<10	3	56
121	7R17991	<0.2	6.10	<5	1230	<5	1.31	<1	2	86	60	0.96	2.03	<10	0.16	199	16	2.53	4	280	28	<5	<20	354	0.08	<10	13	<10	11	89
122	7R17992	<0.2	6.62	<5	1365	<5	1.01	1	2	98	42	0.82	2.04	10	0.08	196	25	2.62	4	190	34	<5	<20	248	0.04	<10	5	<10	15	116
123	7R17993	<0.2	5.39	<5	1320	<5	1.00	<1	<1	100	43	0.78	1.94	<10	0.12	181	315	2.22	3	210	28	<5	<20	293	0.06	<10	9	<10	13	67
124	7R17994	0.4	6.24	<5	540	<5	2.62	<1	2	98	104	1.72	0.89	<10	0.37	366	21	3.00	5	520	22	<5	<20	556	0.21	<10	32	<10	5	70
125	7R17995	<0.2	5.41	<5	525	<5	2.38	<1	2	96	109	1.65	0.90	<10	0.36	340	15	3.06	5	490	18	<5	<20	511	0.21	<10	31	<10	4	67
126	7R17996	<0.2	6.19	<5	755	<5	2.15	<1	2	101	32	1.28	1.27	<10	0.32	319	12	2.68	5	470	24	<5	<20	555	0.17	<10	26	<10	7	59
127	7R17997	0.2	5.71	<5	615	<5	2.30	<1	2	118	77	1.48	0.99	<10	0.38	310	8	2.93	5	500	22	<5	<20	583	0.20	<10	32	<10	4	70

QC DATA:

Repeat:


1	7R17871A	<0.2	6.30	10	1255	<5	0.49	<1	<1	99	45	0.89	2.20	10	0.06	292	152	2.15	3	140	34	<5	<20	96	0.03	<10	2	<10	9	40
10	7R17880	0.4	6.42	<5	675	<5	2.35	<1	2	134	92	1.59	1.12	<10	0.38	379	57	2.78	5	490	26	<5	<20	573	0.20	<10	32	<10	5	58
19	7R17889	<0.2	5.27	10	1040	<5	1.00	<1	<1	145	82	1.07	1.91	10	0.14	201	86	2.22	5	270	28	<5	<20	293	0.07	<10	9	<10	11	45
36	7R17906	<0.2	6.57	<5	845	<5	1.21	1	<1	75	258	1.45	2.31	<10	0.18	335	598	2.04	5	310	28	<5	<20	332	0.11	<10	16	<10	8	109
45	7R17915	0.4	5.93	<5	585	<5	2.56	<1	2	115	95	1.60	0.92	<10	0.41	319	395	2.93	6	530	22	<5	<20	560	0.21	<10	35	<10	3	52
54	7R17924	<0.2	5.97	30	685	<5	1.41	<1	2	97	82	1.77	2.05	20	0.25	308	10	2.16	4	400	22	5	<20	245	0.12	<10	6	<10	11	17
71	7R17941	0.2	6.49	5	720	<5	2.34	<1	2	76	102	1.47	1.37	<10	0.31	337	117	2.67	4	500	22	<5	<20	466	0.20	<10	33	<10	4	46
89	7R17959	0.2	5.08	20	510	<5	2.13	<1	1	111	202	1.58	1.14	<10	0.27	320	937	2.09	5	490	18	<5	<20	353	0.16	<10	29	<10	3	58
106	7R17976	0.4	5.93	5	755	<5	2.01	<1	2	104	42	1.42	1.33	<10	0.32	373	3	2.68	5	470	22	<5	<20	473	0.19	<10	31	<10	6	69
115	7R17985	<0.2	5.96	<5	755	<5	2.09	<1	2	95	28	1.31	1.30	<10	0.36	297	4	2.86	5	460	22	<5	<20	553	0.18	<10	31	<10	6	56
124	7R17994	<0.2	6.30	<5	555	<5	2.70	1	2	89	90	1.71	1.08	10	0.22	335	30	3.14	4	480	26	<5	<20	583	0.18	<10	27	<10	6	80

Resplit:


1	7R17871A	0.2	6.28	10	1250	<5	0.50	<1	<1	94	47	0.90	2.17	10	0.05	290	177	2.28	3	150	34	<5	<20	107	0.03	<10	2	<10	8	41
36	7R17906	0.2	6.41	<5	925	<5	1.34	<1	<1	89	235	1.36	2.31	<10	0.19	328	569	2.25	4	280	26	<5	<20	342	0.11	<10	17	<10	8	97
71	7R17941	0.2	5.94	<5	725	<5	2.13	<1	2	80	101	1.35	1.49	<10	0.28	315	112	2.74	4	470	20	<5	<20	465	0.18	<10	31	<10	5	46
106	7R17976	0.4	5.86	10	775	<5	2.14	<1	2	116	40	1.32	1.23	<10	0.33	372	5	2.56	5	440	26	<5	<20	511	0.18	<10	29	<10	6	61

Et #.	Tag #	Ag	Al%	As	Ba	Bi	Ca%	Cd	Co	Cr	Cu	Fe%	K%	La	Mg%	Mn	Mo	Na%	Ni	P	Pb	Sb	Sn	Sr	Ti%	U	V	W	Y	Zn	
Standard:																															
STSD3		0.4	5.96	25	1365	<5	2.46	<1	16	59	40	3.99	1.36	30	1.25	2489	6	1.10	31	1620	54	<5	<20	259	0.34	<10	116	<10	33	199	
STSD3		0.4	6.01	25	1425	<5	2.57	<1	17	61	40	4.19	1.45	30	1.31	2632	6	1.15	32	1610	56	<5	<20	268	0.36	<10	118	<10	30	204	
STSD3		0.4	5.87	25	1405	<5	2.48	1	17	62	42	4.19	1.39	40	1.29	2552	6	1.14	32	1660	56	<5	<20	263	0.35	<10	118	<10	32	208	
STSD3		0.4	5.72	25	1405	<5	2.39	<1	16	62	42	4.10	1.39	30	1.29	2486	7	1.14	31	1630	56	<5	<20	262	0.34	<10	119	<10	32	203	

JJ/sa/nl
 dt/d 15:19a
 XLS/07

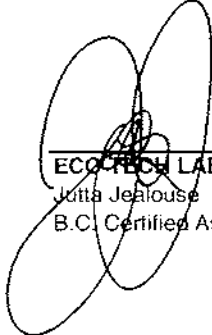

 ECO TECH LABORATORY LTD.
 Julia Jealous
 B.C. Certified Assayer

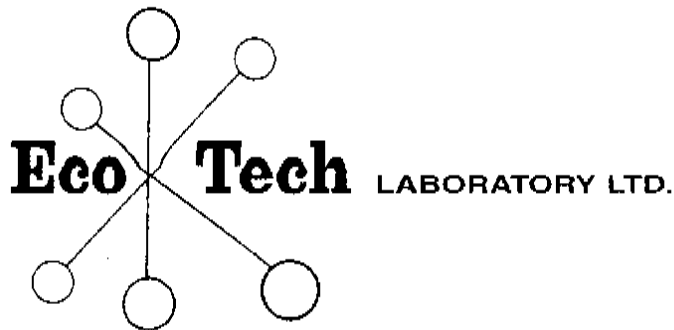

ASSAYING, GEOCHEMISTRY
ANALYTICAL CHEMISTRY
ENVIRONMENTAL TESTING
ISO 9001 Accredited Co.

10041 Dallas Drive, Kamloops, BC V2C 6T4
Phone (250) 573-5700 Fax (250) 573-4557
E-mail: info@ecotechlab.com
www.ecotechlab.com

CERTIFICATE OF ASSAY AK 2007-1509

Pacific Cascade Resources
520 - 700 W. Pender Street
Vancouver, BC
V6C 1G8

18-Oct-07

No. of samples received: 132
Sample Type: Core
Project: Crack Moly
Submitted by: Wesley Raven

ET #.	Tag #	Mo (%)
1	7R17601	0.111
5	7R17605	0.349
7	7R17607	0.064
21	7R17621	0.880
22	7R17622	0.060
24	7R17624	0.091
25	7R17625	0.062
26	7R17626	0.079
44	7R17644	0.062
62	7R17662	0.054
64	7R17664	0.168
67	7R17667	0.053
68	7R17668	0.063
71	7R17671	0.365
82	7R17682	0.062
89	7R17689	3.644
91	7R17691	0.083
92	7R17692	0.197
97	7R17697	0.063
121	7R17721	0.064

QC DATA:

Repeat:

89 7R17689 3.702

Standards:

MP2 0.284
MP2 0.281

JJ/nl
XLS:07

ECO TECH LABORATORY LTD.
Jutta Jealous
B.C. Certified Assayer

ECO TECH LABORATORY LTD.

10041 Dallas Drive

KAMLOOPS, B. C.

V2C 6T4

ICP CERTIFICATE OF ANALYSIS AK 2007- 1509

Pacific Cascade Resources

520 - 700 W. Pender Street

Vancouver, BC

V6C 1G8

Phone: 250-573-5700

Fax : 250-573-4557

No. of samples received: 132

Sample Type: Core

Project: Crack Moly

Submitted by: Wesley Raven

Values in ppm unless otherwise reported

Et #.	Tag #	Ag	Al%	As	Ba	Bi	Ca%	Cd	Co	Cr	Cu	Fe%	K%	La	Mg%	Mn	Mo	Na%	Ni	P	Pb	Sb	Sn	Sr	Ti%	U	V	W	Y	Zn
1	7R17601	0.3	4.23	65	530	<5	1.23	<1	<1	70	108	0.83	1.67	<10	0.17	208	984	1.61	3	320	24	<5	<20	254	0.07	<10	11	<10	9	46
2	7R17602	<0.2	4.45	15	490	<5	1.69	<1	2	123	51	1.36	1.10	<10	0.28	299	53	3.21	4	420	22	<5	<20	554	0.16	<10	23	<10	3	83
3	7R17603	<0.2	5.16	10	490	<5	2.26	<1	2	143	16	1.41	0.92	<10	0.27	246	50	3.09	6	460	24	<5	<20	602	0.18	<10	25	<10	3	47
4	7R17604	<0.2	4.61	10	530	<5	1.83	<1	2	138	27	1.38	1.12	<10	0.28	251	196	2.84	5	420	22	<5	<20	524	0.16	<10	22	<10	3	42
5	7R17605	<0.2	4.44	15	500	<5	1.76	<1	<1	133	36	1.33	1.26	<10	0.27	324	3334	2.43	5	410	22	<5	<20	450	0.15	<10	19	<10	4	48
6	7R17606	<0.2	4.50	50	545	<5	1.67	<1	2	137	77	1.50	1.11	<10	0.28	299	180	2.61	5	460	22	<5	<20	484	0.16	<10	24	<10	3	48
7	7R17607	<0.2	4.82	10	845	<5	1.26	<1	5	22	126	2.66	3.26	30	0.55	566	642	1.60	14	820	28	<5	<20	211	0.23	<10	45	<10	16	88
8	7R17608	<0.2	4.83	10	585	<5	1.79	<1	2	136	34	1.51	1.17	<10	0.31	293	98	3.01	6	430	24	<5	<20	552	0.17	<10	24	<10	3	68
9	7R17609	<0.2	5.03	10	615	<5	2.06	<1	2	131	19	1.33	1.19	<10	0.27	245	69	2.91	5	400	24	<5	<20	545	0.16	<10	20	<10	4	48
10	7R17610	<0.2	5.09	5	610	<5	2.28	<1	2	133	22	1.32	0.86	<10	0.30	221	181	2.93	5	400	22	<5	<20	610	0.18	<10	21	<10	3	83
11	7R17611	0.2	4.64	10	465	<5	1.67	1	1	192	25	1.52	0.97	<10	0.28	259	437	2.87	6	460	24	<5	<20	538	0.18	<10	23	<10	3	115
12	7R17612	<0.2	4.33	15	505	<5	1.57	<1	1	144	26	1.33	0.93	<10	0.28	267	216	2.85	6	410	20	<5	<20	531	0.16	<10	20	<10	2	44
13	7R17613	<0.2	4.55	5	545	<5	2.06	<1	2	163	19	1.38	1.02	<10	0.31	247	76	3.14	6	440	22	<5	<20	580	0.19	<10	24	<10	2	50
14	7R17614	0.2	4.52	5	580	<5	1.96	<1	2	129	20	1.36	0.84	<10	0.33	253	19	3.14	5	420	22	<5	<20	616	0.18	<10	23	<10	2	49
15	7R17615	<0.2	4.25	5	530	<5	1.87	<1	2	146	41	1.34	0.83	<10	0.29	257	149	3.05	5	420	22	<5	<20	590	0.17	<10	23	<10	2	47
16	7R17616	0.2	5.46	10	675	<5	2.25	<1	2	134	27	1.59	1.05	<10	0.39	296	72	3.55	5	510	26	<5	<20	707	0.21	<10	28	<10	3	72
17	7R17617	<0.2	4.71	5	565	<5	2.01	<1	2	147	18	1.41	0.86	<10	0.32	303	166	3.07	6	420	26	<5	<20	612	0.18	<10	22	<10	2	74
18	7R17618	<0.2	4.48	10	620	<5	0.69	<1	<1	100	69	0.96	2.75	<10	0.11	254	388	2.03	3	210	30	<5	<20	216	0.04	<10	6	<10	13	52
19	7R17619	<0.2	4.45	5	610	<5	1.61	<1	1	156	42	1.32	1.16	<10	0.28	322	362	2.85	5	390	24	<5	<20	552	0.15	<10	20	<10	4	48
20	7R17620	<0.2	4.45	5	550	<5	1.76	<1	1	133	31	1.34	0.85	<10	0.31	272	454	2.88	5	420	24	<5	<20	579	0.17	<10	20	<10	2	43
21	7R17621	<0.2	4.26	5	565	<5	1.17	<1	<1	168	24	1.32	0.89	<10	0.30	245	835	2.73	5	390	22	<5	<20	583	0.16	<10	23	<10	2	42
22	7R17622	<0.2	4.47	5	580	<5	1.68	<1	<1	149	19	1.40	0.92	<10	0.30	273	584	3.10	5	510	22	<5	<20	581	0.17	<10	22	<10	3	42
23	7R17623	<0.2	4.93	10	620	<5	1.74	<1	1	135	21	1.46	1.06	<10	0.32	271	371	3.00	6	440	22	<5	<20	589	0.17	<10	22	<10	3	43
24	7R17624	<0.2	4.32	10	505	<5	1.49	<1	<1	165	66	1.40	0.95	10	0.28	240	874	2.48	5	390	24	<5	<20	506	0.15	<10	19	<10	3	40
25	7R17625	0.2	5.21	10	875	<5	1.29	<1	5	22	129	2.84	3.30	30	0.56	597	617	1.81	17	890	32	<5	<20	219	0.24	<10	46	<10	16	90

Et #.	Tag #	Ag	Al%	As	Ba	Bi	Ca%	Cd	Co	Cr	Cu	Fe%	K%	La	Mg%	Mn	Mo	Na%	Ni	P	Pb	Sb	Sn	Sr	Ti%	U	V	W	Y	Zr
26	7R17626	<0.2	4.45	10	665	<5	1.77	<1	1	136	37	1.43	1.05	<10	0.30	303	758	2.96	5	420	26	<5	<20	588	0.18	<10	22	<10	3	40
27	7R17627	<0.2	4.59	5	615	<5	1.67	<1	2	161	41	1.31	1.08	10	0.29	254	23	2.85	5	430	22	<5	<20	596	0.16	<10	20	<10	3	40
28	7R17628	<0.2	4.75	15	575	<5	1.73	<1	2	159	49	1.36	1.22	<10	0.28	309	111	2.82	5	460	30	<5	<20	553	0.15	<10	21	<10	3	50
29	7R17629	<0.2	5.10	10	520	<5	1.58	<1	1	176	121	1.59	1.58	10	0.28	281	491	2.46	5	530	26	<5	<20	462	0.15	<10	25	<10	4	70
30	7R17630	<0.2	7.52	15	560	<5	1.94	<1	2	165	82	1.54	1.68	<10	0.29	278	183	2.59	6	440	26	<5	<20	548	0.16	<10	27	<10	3	40
31	7R17631	0.4	6.15	60	590	<5	2.21	<1	1	146	50	1.31	1.23	<10	0.31	272	183	2.77	5	450	24	<5	<20	543	0.16	<10	25	<10	3	40
32	7R17632	<0.2	6.82	10	570	<5	2.45	<1	2	156	13	1.44	0.88	<10	0.32	250	130	2.94	6	440	24	<5	<20	615	0.18	<10	22	<10	3	47
33	7R17633	<0.2	6.42	5	645	<5	2.28	<1	2	132	28	1.40	1.00	<10	0.29	257	63	2.82	5	400	24	<5	<20	587	0.17	<10	20	<10	3	40
34	7R17634	0.4	5.71	5	560	<5	2.27	<1	1	207	21	1.30	0.84	<10	0.29	240	390	2.84	5	380	24	<5	<20	617	0.16	<10	20	<10	3	44
35	7R17635	<0.2	6.60	10	625	<5	2.54	<1	2	153	23	1.39	0.89	<10	0.31	255	89	3.08	6	420	24	<5	<20	635	0.18	<10	22	<10	3	50
36	7R17636	0.4	5.15	10	545	<5	2.25	<1	2	285	39	1.59	0.83	<10	0.30	281	251	3.09	7	460	26	<5	<20	635	0.18	<10	24	<10	2	40
37	7R17637	0.2	5.29	10	615	<5	2.20	<1	2	182	30	1.46	0.91	<10	0.31	292	378	3.20	6	430	26	<5	<20	667	0.18	<10	22	<10	3	51
38	7R17638	0.2	5.28	10	680	<5	2.24	<1	2	164	29	1.48	0.98	<10	0.34	327	95	3.13	6	460	28	<5	<20	681	0.19	<10	22	<10	3	55
39	7R17639	0.2	5.15	5	625	<5	2.18	<1	2	173	31	1.54	1.07	<10	0.32	299	58	3.21	6	470	26	<5	<20	660	0.19	<10	22	<10	3	51
40	7R17640	0.6	5.08	10	600	<5	2.11	<1	3	218	286	1.74	0.90	<10	0.34	277	86	3.11	7	440	28	<5	<20	640	0.18	<10	24	<10	2	61
41	7R17641	<0.2	5.06	10	615	<5	1.82	<1	1	151	147	1.43	0.99	<10	0.32	259	181	2.88	5	420	26	<5	<20	616	0.17	<10	25	<10	2	51
42	7R17642	<0.2	5.00	5	615	<5	2.16	<1	2	177	32	1.53	0.88	<10	0.33	289	25	3.25	7	450	26	<5	<20	652	0.19	<10	23	<10	3	50
43	7R17643	1.4	4.79	10	610	<5	1.83	<1	4	172	52	1.64	0.98	<10	0.30	334	256	3.01	6	430	82	<5	<20	633	0.17	<10	22	<10	2	60
44	7R17644	0.2	5.61	10	880	<5	1.49	<1	5	21	129	2.80	3.22	30	0.57	639	628	1.63	17	870	36	<5	<20	271	0.24	<10	44	<10	16	87
45	7R17645	0.6	4.69	5	555	<5	2.06	<1	2	175	433	1.42	0.84	<10	0.29	285	130	2.67	5	390	24	<5	<20	598	0.16	<10	20	<10	2	54
46	7R17646	<0.2	5.15	5	635	<5	2.21	<1	2	216	19	1.50	1.00	<10	0.32	325	349	2.88	7	430	24	<5	<20	609	0.18	<10	23	<10	3	72
47	7R17647	<0.2	5.12	10	585	<5	2.29	<1	2	177	22	1.50	0.89	<10	0.33	326	89	3.04	6	460	26	<5	<20	621	0.19	<10	23	<10	2	58
48	7R17648	<0.2	5.09	10	550	<5	2.28	<1	2	155	49	1.54	0.93	<10	0.32	310	209	2.84	5	480	24	<5	<20	590	0.18	<10	24	<10	2	53
49	7R17649	<0.2	5.04	5	580	<5	2.15	<1	2	173	28	1.46	0.89	<10	0.32	312	86	3.00	6	450	24	<5	<20	617	0.17	<10	21	<10	2	52
50	7R17650	<0.2	6.21	10	680	<5	2.61	<1	2	182	24	1.63	1.14	<10	0.36	329	201	3.44	6	480	30	<5	<20	693	0.20	<10	25	<10	3	52
51	7R17651	<0.2	4.96	10	580	<5	2.35	<1	2	185	33	1.41	0.84	<10	0.28	299	23	3.02	6	430	24	<5	<20	628	0.18	<10	21	<10	2	46
52	7R17652	<0.2	5.38	10	720	<5	2.03	<1	2	170	23	1.40	1.32	<10	0.28	327	41	3.10	6	410	28	<5	<20	576	0.17	<10	19	<10	5	55
53	7R17653	<0.2	5.89	5	595	<5	2.58	<1	2	180	28	1.50	0.88	<10	0.33	354	9	3.37	6	460	26	<5	<20	640	0.19	<10	23	<10	3	57
54	7R17654	<0.2	4.86	10	500	<5	2.11	<1	2	161	46	1.47	0.87	<10	0.29	364	58	2.94	5	420	26	<5	<20	575	0.17	<10	20	<10	3	57
55	7R17655	0.2	5.22	10	480	<5	2.15	<1	2	144	40	1.45	0.89	<10	0.30	373	61	3.08	6	440	24	<5	<20	587	0.17	<10	20	<10	3	75
56	7R17656	1.0	5.71	10	1420	<5	0.78	<1	<1	114	45	0.86	3.10	10	0.06	146	61	2.26	3	160	36	<5	<20	180	0.03	<10	2	<10	12	55
57	7R17657	<0.2	5.05	10	550	<5	2.23	<1	2	136	17	1.48	0.90	<10	0.33	407	117	2.94	5	550	24	<5	<20	593	0.18	<10	21	<10	3	66
58	7R17658	<0.2	4.67	5	525	<5	1.99	<1	2	158	23	1.62	0.88	<10	0.30	421	136	2.83	6	410	22	<5	<20	547	0.18	<10	23	<10	3	63
59	7R17659	<0.2	4.63	10	1375	<5	0.73	<1	1	77	36	0.62	3.26	10	0.05	126	98	2.16	2	150	34	<5	<20	192	0.03	<10	2	<10	11	54
60	7R17660	<0.2	4.16	15	1260	<5	0.56	<1	<1	155	66	0.73	3.44	10	0.05	122	320	1.30	4	180	40	<5	<20	152	0.02	<10	3	<10	10	29
61	7R17661	<0.2	5.97	10	1635	<5	0.64	<1	<1	76	72	0.67	4.05	20	0.07	116	88	1.60	3	190	40	<5	<20	203	0.03	<10	3	<10	10	28
62	7R17662	0.8	5.76	10	1390	10	0.68	9	<1	150	191	0.93	3.57	20	0.07	138	536	1.31	4	170	72	<5	<20	158	0.03	<10	5	<10	9	822
63	7R17663	0.4	6.24	10	1495	<5	0.68	<1	<1	96	35	0.66	3.81	20	0.07	127	174	1.55	3	170	44	<5	<20	212	0.03	<10	3	<10	10	29
64	7R17664	<0.2	4.33	10	1470	<5	0.49	1	<1	105	27	0.55	3.76	20	0.05	113	1451	1.50	3	150	38	<5	<20	218	0.02	<10	3	<10	9	59
65	7R17665	<0.2	4.79	10	1130	<5	0.64	<1	<1	116	51	0.63	3.21	10	0.04	104	201	1.60	3	130	32	<5	<20	183	0.02	<10	3	<10	7	48

Et #.	Tag #	Ag	Al%	As	Ba	Bi	Ca%	Cd	Co	Cr	Cu	Fe%	K%	La	Mg%	Mn	Mo	Na%	Ni	P	Pb	Sb	Sn	Sr	Ti%	U	V	W	Y	Zn
66	7R17666	<0.2	5.23	5	1210	<5	0.76	<1	<1	125	57	0.85	3.36	10	0.06	124	359	1.85	3	160	34	<5	<20	199	0.03	<10	4	10	10	58
67	7R17667	<0.2	5.28	5	1295	<5	0.79	<1	<1	135	36	0.79	3.03	10	0.06	154	515	2.08	3	170	34	<5	<20	210	0.04	<10	4	<10	11	34
68	7R17668	<0.2	5.66	10	910	<5	1.55	<1	6	21	131	3.01	3.40	30	0.59	689	640	1.79	18	970	34	<5	<20	305	0.28	<10	49	<10	17	96
69	7R17669	<0.2	4.83	5	1130	<5	0.80	<1	<1	128	44	1.03	2.67	10	0.09	213	291	2.34	4	190	32	<5	<20	261	0.05	<10	6	<10	11	40
70	7R17670	<0.2	4.71	10	980	<5	0.70	<1	<1	128	34	0.94	2.42	<10	0.08	179	143	2.45	4	160	32	<5	<20	236	0.05	<10	8	<10	10	46
71	7R17671	<0.2	4.97	10	1050	<5	0.80	4	<1	148	54	1.02	2.70	10	0.05	210	3463	2.29	4	210	34	<5	<20	202	0.04	<10	5	<10	11	256
72	7R17672	<0.2	4.99	5	1305	<5	0.75	7	<1	107	67	0.92	2.97	20	0.08	151	359	2.19	3	140	34	<5	<20	232	0.04	<10	5	<10	14	268
73	7R17673	<0.2	4.59	15	1010	<5	0.97	<1	<1	105	35	1.05	2.26	<10	0.15	234	126	2.56	4	250	34	<5	<20	377	0.09	<10	13	<10	9	44
74	7R17674	<0.2	4.62	5	1040	<5	0.89	<1	<1	91	26	1.05	2.33	<10	0.14	235	133	2.49	3	200	30	<5	<20	354	0.08	<10	13	<10	9	39
75	7R17675	<0.2	4.35	5	770	<5	0.95	<1	<1	107	46	1.41	1.74	<10	0.18	314	206	2.55	3	220	30	<5	<20	371	0.11	<10	14	<10	7	49
76	7R17676	<0.2	4.99	10	1055	<5	1.30	<1	<1	69	40	1.32	2.06	10	0.20	310	152	2.74	2	290	32	<5	<20	421	0.11	<10	14	<10	7	55
77	7R17677	0.2	4.95	5	1035	<5	1.31	<1	1	85	29	1.07	2.32	<10	0.16	252	178	2.60	3	250	30	<5	<20	357	0.09	<10	11	<10	9	39
78	7R17678	<0.2	5.03	10	970	<5	1.04	<1	1	104	35	1.30	2.20	10	0.19	305	123	2.59	4	280	32	<5	<20	343	0.11	<10	13	<10	7	47
79	7R17679	<0.2	5.00	10	1265	<5	0.96	<1	1	110	28	1.11	2.54	<10	0.14	234	130	2.55	4	220	36	<5	<20	345	0.07	<10	9	<10	12	36
80	7R17680	<0.2	5.17	10	1380	<5	0.92	<1	<1	88	81	0.92	2.90	10	0.10	191	296	2.47	3	200	36	<5	<20	308	0.06	<10	7	<10	13	47
81	7R17681	<0.2	4.62	10	865	<5	1.21	<1	1	89	32	1.18	1.82	<10	0.19	286	91	2.62	3	290	28	<5	<20	420	0.10	<10	13	<10	7	42
82	7R17682	0.2	4.71	10	980	<5	1.04	<1	<1	113	37	0.99	2.11	<10	0.12	229	603	2.16	3	210	30	<5	<20	302	0.07	<10	9	<10	10	41
83	7R17683	<0.2	5.06	10	1090	<5	1.26	<1	1	93	23	1.05	2.29	10	0.15	263	115	2.59	3	270	30	<5	<20	350	0.08	<10	10	<10	9	42
84	7R17684	<0.2	6.24	10	1525	<5	1.01	<1	<1	79	39	0.91	3.02	10	0.11	214	156	2.38	3	200	36	<5	<20	297	0.05	<10	6	<10	12	46
85	7R17685	0.4	6.27	5	1345	<5	1.07	<1	1	108	53	1.01	2.79	<10	0.11	234	172	2.50	4	190	34	<5	<20	301	0.06	<10	8	<10	13	72
86	7R17686	2.2	4.80	10	1215	<5	1.11	<1	1	91	45	0.96	2.57	<10	0.12	238	38	2.54	3	270	32	<5	<20	293	0.06	<10	8	<10	10	51
87	7R17687	1.0	4.74	10	1450	<5	0.68	<1	<1	132	40	0.75	3.12	<10	0.06	147	178	2.23	4	140	32	<5	<20	204	0.03	<10	6	<10	12	54
88	7R17688	<0.2	4.90	5	1400	<5	0.63	<1	<1	106	38	0.72	3.16	10	0.04	134	9	2.44	3	150	34	<5	<20	159	0.02	<10	2	<10	14	44
89	7R17689	<0.2	4.47	15	1135	<5	0.70	1	<1	244	39	0.82	2.49	<10	<0.01	334	>10000	2.12	4	260	26	<5	<20	139	0.03	<10	2	<10	11	106
90	7R17690	<0.2	6.38	10	1440	<5	0.84	<1	<1	76	23	0.70	2.98	20	0.06	180	55	2.50	3	150	34	<5	<20	145	0.03	<10	2	<10	11	82
91	7R17691	<0.2	4.92	15	1210	<5	0.65	2	<1	131	119	1.20	2.88	10	0.06	199	742	2.01	3	190	30	<5	<20	144	0.03	<10	3	<10	10	109
92	7R17692	0.4	4.02	20	1265	<5	0.70	<1	<1	219	52	0.82	3.01	<10	0.05	171	1885	1.52	5	140	32	<5	<20	162	0.02	<10	3	<10	9	84
93	7R17693	<0.2	4.98	10	1320	<5	0.68	<1	<1	105	33	0.83	2.93	10	0.05	165	123	2.25	3	160	36	<5	<20	155	0.03	<10	4	<10	10	45
94	7R17694	<0.2	5.18	10	1225	<5	0.83	<1	<1	111	24	1.38	2.60	10	0.10	320	204	2.63	3	210	32	<5	<20	172	0.06	<10	8	<10	10	59
95	7R17695	<0.2	5.22	10	1285	<5	0.72	<1	<1	100	30	0.88	2.82	10	0.05	188	35	2.63	3	160	34	<5	<20	149	0.03	<10	3	<10	13	48
96	7R17696	0.4	4.92	5	1315	<5	0.72	<1	1	101	23	0.89	2.94	10	0.07	196	9	2.42	3	160	32	<5	<20	169	0.03	<10	3	<10	12	41
97	7R17697	<0.2	5.76	10	905	<5	1.55	<1	5	20	130	2.77	3.29	30	0.57	611	624	1.66	16	850	34	<5	<20	309	0.25	<10	47	<10	16	88
98	7R17698	<0.2	6.04	15	1705	<5	0.76	<1	<1	86	35	0.83	3.78	10	0.05	160	199	2.49	3	290	40	<5	<20	195	0.02	<10	3	<10	14	62
99	7R17699	0.4	4.93	15	1390	<5	0.54	1	1	113	55	0.87	2.99	10	0.04	159	29	2.49	3	140	34	<5	<20	157	0.02	<10	2	<10	14	76
100	7R17700	0.6	4.45	10	1420	<5	0.43	<1	<1	107	27	0.75	3.12	10	0.04	152	406	2.39	3	140	40	<5	<20	157	0.02	<10	3	<10	15	39
101	7R17701	0.2	5.05	10	1440	<5	0.61	<1	<1	111	27	0.85	3.20	10	0.04	165	19	2.62	4	140	36	<5	<20	153	0.02	<10	2	<10	15	50
102	7R17702	<0.2	4.78	10	1445	<5	0.52	<1	<1	119	23	0.85	3.17	10	0.04	164	121	2.71	3	130	40	<5	<20	143	0.02	<10	1	<10	13	43
103	7R17703	0.2	4.79	5	1410	<5	0.51	<1	<1	107	25	0.87	3.04	10	0.04	171	67	2.60	3	140	36	<5	<20	156	0.03	<10	2	<10	12	60
104	7R17704	0.2	4.93	10	1370	<5	0.64	2	<1	118	43	0.94	3.09	10	0.05	181	45	2.45	4	170	38	<5	<20	160	0.03	<10	3	<10	14	104
105	7R17705	0.2	4.59	10	1475	<5	0.55	1	<1	110	44	0.85	3.17	10	0.05	155	58	2.39	3	140	36	<5	<20	167	0.02	<10	2	<10	13	83

Et #.	Tag #	Ag	Al%	As	Ba	Bi	Ca%	Cd	Co	Cr	Cu	Fe%	K%	La	Mg%	Mn	Mo	Na%	Ni	P	Pb	Sb	Sn	Sr	Ti%	U	V	W	Y	Zn
106	7R17706	<0.2	4.85	25	1330	<5	0.67	<1	<1	123	45	0.83	2.90	10	0.05	172	63	2.45	3	150	34	<5	<20	158	0.02	<10	1	<10	13	46
107	7R17707	0.2	4.89	10	1310	<5	0.67	<1	<1	106	43	0.83	2.87	10	0.06	176	32	2.48	3	140	34	<5	<20	154	0.02	<10	1	<10	13	56
108	7R17708	<0.2	4.89	5	1295	<5	0.68	<1	<1	107	23	0.78	2.85	10	0.05	159	7	2.40	3	140	30	<5	<20	151	0.02	<10	<1	<10	13	52
109	7R17709	0.4	4.75	5	1340	<5	0.62	<1	<1	90	30	0.76	2.95	10	0.05	176	7	2.40	2	140	34	<5	<20	154	0.03	<10	2	<10	14	64
110	7R17710	<0.2	4.60	5	1320	<5	0.63	<1	<1	103	20	0.76	2.91	10	0.05	182	117	2.34	3	140	34	<5	<20	155	0.03	<10	1	<10	10	41
111	7R17711	<0.2	4.78	10	1300	<5	0.63	<1	<1	64	26	0.76	2.87	10	0.05	180	19	2.33	2	140	34	<5	<20	162	0.03	<10	2	<10	10	39
112	7R17712	<0.2	4.75	10	1335	<5	0.65	<1	<1	90	22	0.77	2.88	10	0.05	197	136	2.48	3	160	32	<5	<20	169	0.03	<10	2	<10	11	51
113	7R17713	0.2	4.19	10	1140	10	0.59	1	<1	71	120	0.84	2.60	<10	0.05	112	60	1.85	3	130	30	<5	<20	156	0.03	<10	4	<10	10	74
114	7R17714	0.4	4.80	5	1170	<5	0.95	<1	<1	80	65	0.90	2.50	10	0.10	208	12	2.33	3	200	30	<5	<20	235	0.06	<10	5	<10	11	54
115	7R17715	0.4	4.25	10	795	<5	1.30	<1	1	94	46	1.14	1.84	<10	0.18	254	18	2.71	4	290	24	<5	<20	347	0.10	<10	14	<10	8	54
116	7R17716	0.4	4.13	5	710	<5	1.77	<1	2	109	180	1.93	1.26	<10	0.43	368	60	2.49	6	520	20	<5	<20	465	0.23	<10	33	<10	4	62
117	7R17717	<0.2	4.52	10	1290	<5	0.48	<1	<1	71	58	0.68	3.40	20	0.05	119	13	1.85	2	160	32	<5	<20	201	0.03	<10	2	<10	12	75
118	7R17718	0.4	4.74	10	1320	<5	0.54	<1	<1	102	68	0.75	3.48	20	0.04	109	194	1.76	3	170	36	<5	<20	188	0.03	<10	1	<10	12	53
119	7R17719	0.4	4.63	15	1335	<5	0.56	<1	<1	56	35	0.61	3.56	20	0.05	115	57	1.90	2	160	36	<5	<20	188	0.03	<10	1	<10	10	88
120	7R17720	0.2	4.94	20	1160	<5	0.72	2	<1	81	62	0.72	3.13	20	0.05	131	28	1.83	2	160	32	<5	<20	188	0.03	<10	2	<10	11	136
121	7R17721	0.2	5.47	10	855	<5	1.54	<1	5	19	127	2.73	3.20	30	0.56	634	631	1.85	16	880	30	<5	<20	320	0.26	<10	44	<10	16	92
122	7R17722	0.2	4.81	10	495	<5	1.74	<1	2	93	98	2.01	1.34	<10	0.30	437	166	2.43	5	480	22	<5	<20	441	0.17	<10	22	<10	3	93
123	7R17723	<0.2	3.99	125	340	<5	1.55	<1	2	156	85	1.67	1.21	<10	0.22	363	183	1.74	6	1340	20	<5	<20	271	0.12	<10	17	<10	11	66
124	7R17724	0.2	4.70	10	1280	<5	0.70	<1	<1	67	36	0.73	3.11	20	0.07	158	50	2.02	2	190	34	<5	<20	277	0.04	<10	4	<10	11	74
125	7R17725	0.2	5.13	10	620	<5	1.66	<1	2	99	160	2.40	1.89	<10	0.30	553	215	2.30	5	510	26	<5	<20	415	0.17	<10	23	<10	3	89
126	7R17726	0.2	4.46	10	540	<5	1.64	<1	2	114	84	2.09	1.36	<10	0.27	507	162	2.35	5	390	24	<5	<20	430	0.16	<10	18	<10	3	118
127	7R17727	0.2	4.66	15	675	<5	1.09	10	2	111	269	2.03	1.82	<10	0.26	337	175	2.06	4	380	22	<5	<20	392	0.14	<10	17	<10	4	810
128	7R17728	0.4	4.73	10	505	<5	1.70	2	1	63	98	1.64	1.26	<10	0.27	385	86	2.41	4	440	20	<5	<20	429	0.16	<10	20	<10	3	230
129	7R17729	0.4	4.74	15	710	<5	1.11	2	1	97	134	1.98	1.70	<10	0.27	426	347	2.08	5	470	24	<5	<20	385	0.15	<10	19	<10	5	239
130	7R17730	0.2	4.82	10	595	<5	1.48	2	1	51	142	1.46	1.50	10	0.22	345	63	2.44	4	410	24	<5	<20	412	0.13	<10	18	<10	7	148
131	7R17731	1.4	4.73	50	620	20	1.38	2	2	107	304	1.85	1.85	<10	0.21	337	276	1.60	4	410	30	<5	<20	273	0.12	<10	16	<10	5	126
132	7R17732	0.4	4.64	15	345	<5	1.44	<1	2	39	123	1.63	1.18	10	0.20	327	18	2.96	2	370	24	<5	<20	217	0.09	<10	5	<10	11	44

QC DATA:


Repeat:

1	7R17601	0.2	4.46	65	520	<5	1.24	<1	<1	69	103	0.83	1.62	<10	0.17	208	1063	1.73	3	320	26	<5	<20	261	0.07	<10	10	<10	10	45
10	7R17610	<0.2	4.70	5	615	<5	2.13	<1	2	129	23	1.36	0.89	<10	0.33	224	190	3.15	5	420	22	<5	<20	621	0.18	<10	23	<10	2	76
19	7R17619	<0.2	4.75	10	645	<5	1.71	<1	1	161	39	1.37	1.21	<10	0.30	348	360	3.00	5	420	26	<5	<20	578	0.16	<10	20	<10	3	53
36	7R17636	<0.2	4.70	10	540	<5	2.19	<1	2	268	40	1.57	0.82	<10	0.28	268	278	2.95	7	440	26	<5	<20	610	0.18	<10	22	<10	2	47
45	7R17645	0.6	4.73	5	580	<5	2.08	<1	2	165	457	1.53	0.85	<10	0.31	303	124	2.78	7	440	26	<5	<20	634	0.18	<10	22	<10	2	59
54	7R17654	<0.2	4.74	10	480	<5	2.06	<1	2	155	48	1.44	0.87	<10	0.28	357	60	2.84	5	410	24	<5	<20	549	0.17	<10	21	<10	3	60
71	7R17671	<0.2	5.10	10	1085	<5	0.90	4	<1	147	55	1.10	2.72	10	0.06	223	3402	2.36	4	240	36	<5	<20	218	0.05	<10	6	<10	11	270
80	7R17680	<0.2	5.09	10	1370	<5	0.98	<1	<1	86	81	0.91	2.92	<10	0.10	185	294	2.52	3	180	30	<5	<20	291	0.06	<10	7	<10	12	43
89	7R17689	<0.2	4.35	10	1085	<5	0.76	1	<1	236	37	0.80	2.34	<10	<0.01	321	>10000	1.92	3	230	24	<5	<20	130	0.02	<10	2	<10	11	108
106	7R17706	<0.2	4.73	20	1340	<5	0.64	<1	<1	126	45	0.81	2.93	<10	0.04	165	60	2.38	4	140	34	<5	<20	153	0.02	<10	1	<10	13	47
115	7R17715	<0.2	4.22	5	800	<5	1.34	<1	1	84	46	1.13	1.83	<10	0.19	260	17	2.64	4	290	24	<5	<20	338	0.10	<10	13	<10	8	58
124	7R17724	0.2	4.90	15	1285	<5	0.73	<1	<1	59	34	0.75	3.12	10	0.07	173	51	2.09	3	200	34	<5	<20	280	0.04	<10	3	<10	11	73

Et #.	Tag #	Ag	Al%	As	Ba	Bi	Ca%	Cd	Co	Cr	Cu	Fe%	K%	La	Mg%	Mn	Mo	Na%	Ni	P	Pb	Sb	Sn	Sr	Ti%	U	V	W	Y	Zn	
Resplit:																															
1	7R17601	0.2	4.30	25	530	<5	1.30	<1	<1	66	100	0.79	1.54	<10	0.16	206	1011	1.76	3	330	24	<5	<20	271	0.07	<10	10	<10	10	46	
36	7R17636	<0.2	4.91	5	525	<5	2.10	<1	2	277	37	1.54	0.84	<10	0.30	278	264	3.12	8	440	24	<5	<20	603	0.17	<10	24	<10	2	48	
71	7R17671	0.2	4.70	10	1035	<5	0.71	3	<1	141	47	0.95	2.92	10	0.03	202	3543	2.28	3	190	32	<5	<20	206	0.04	<10	5	<10	12	242	
106	7R17706	0.2	4.94	20	1315	<5	0.63	<1	<1	119	41	0.86	2.82	10	0.05	189	66	2.31	3	170	36	<5	<20	169	0.03	<10	1	<10	13	49	
Standard:																															
Pb113A		0.5	5.77	30	1390	<5	2.49	<1	16	58	41	4.20	1.36	40	1.24	2548	5	1.13	30	1680	56	<5	<20	263	0.32	<10	108	<10	33	195	
Pb113A		0.4	5.92	25	1320	<5	2.26	<1	16	60	42	4.00	1.41	40	1.29	2514	4	1.14	30	1710	54	<5	<20	262	0.32	<10	120	<10	31	201	
Pb113A		0.4	5.88	30	1335	<5	2.33	<1	16	57	41	4.19	1.40	40	1.30	2609	9	1.16	31	1710	56	<5	<20	266	0.34	<10	120	<10	30	198	
Pb113A		0.5	5.61	25	1385	<5	2.44	<1	17	62	42	4.14	1.39	30	1.28	2500	7	1.16	31	1630	54	<5	<20	257	0.34	<10	118	<10	32	200	

ICP: 4 ACID DIGEST/ICP-FINISH
 AG: 4 ACID DIGEST/AA-FINISH

JJ/hl
 ut.tr1509S
 XLS/07

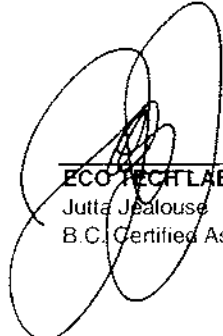

ECO TECH LABORATORY LTD.
 Jutta Jealous
 B.C. Certified Assayer

ECO TECH LABORATORY LTD.

10041 Dallas Drive

KAMLOOPS, B.C.

V2C 6T4

ICP CERTIFICATE OF ANALYSIS AK 2007- 1492

Pacific Cascade Resources

520 - 700 W. Pender Street

Vancouver, BC

V6C 1G8

Phone: 250-573-5700

Fax : 250-573-4557

No. of samples received: 28

Sample Type: Core


Project: Crack Moly

Values in ppm unless otherwise reported


Et #.	Tag #	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
1	7R17571	0.8	0.47	15	100	<5	0.53	<1	3	47	518	1.48	<10	0.18	176	82	0.03	3	300	18	5	<20	31	0.04	<10	9	<10	<1	54
2	7R17572	<0.2	0.33	20	60	<5	0.60	<1	1	69	18	0.66	<10	0.07	135	9	0.03	3	80	20	<5	<20	35	0.02	<10	4	<10	3	26
3	7R17573	<0.2	0.63	20	185	10	0.27	<1	3	64	66	1.26	<10	0.26	179	95	0.06	3	310	18	5	<20	19	0.09	<10	14	<10	<1	32
4	7R17574	<0.2	0.17	20	35	5	0.32	<1	<1	58	28	0.38	<10	0.01	61	132	0.04	2	40	18	<5	<20	13	<0.01	<10	1	<10	9	44
5	7R17575	<0.2	0.15	20	30	<5	0.28	<1	<1	44	18	0.30	<10	0.02	65	24	0.03	1	40	16	<5	<20	5	<0.01	<10	<1	<10	7	30
6	7R17576	0.2	0.15	20	35	<5	0.30	<1	1	49	207	0.87	<10	<0.01	42	265	0.02	<1	50	14	<5	<20	15	<0.01	<10	<1	<10	6	52
7	7R17577	<0.2	0.11	15	25	<5	0.32	1	<1	39	35	0.29	<10	0.02	50	8	0.03	2	40	14	10	<20	10	<0.01	<10	2	<10	7	71
8	7R17578	<0.2	0.14	15	30	<5	0.35	<1	<1	59	37	0.36	<10	<0.01	58	99	0.03	1	40	14	<5	<20	11	<0.01	<10	<1	<10	7	39
9	7R17579	<0.2	0.14	15	30	<5	0.27	<1	<1	51	21	0.28	<10	0.03	51	126	0.03	3	40	16	10	<20	17	<0.01	<10	2	<10	6	20
10	7R17580	0.2	0.15	10	30	<5	0.29	<1	<1	59	38	0.37	<10	<0.01	57	232	0.04	<1	30	14	<5	<20	7	<0.01	<10	<1	<10	7	26
11	7R17581	0.2	0.15	15	35	<5	0.29	1	<1	67	90	0.47	<10	<0.01	54	194	0.03	2	30	14	<5	<20	12	<0.01	<10	<1	<10	6	64
12	7R17582	0.4	0.17	20	30	<5	0.26	2	1	56	257	0.77	<10	<0.01	37	106	0.02	2	40	18	<5	<20	9	<0.01	<10	1	<10	5	96
13	7R17583	0.3	0.13	15	30	<5	0.46	<1	<1	61	127	0.45	<10	<0.01	46	111	0.03	2	30	16	<5	<20	21	<0.01	<10	<1	<10	5	61
14	7R17584	<0.2	0.12	15	30	<5	0.41	1	<1	48	65	0.32	<10	<0.01	50	72	0.03	1	30	16	<5	<20	20	<0.01	<10	<1	<10	5	76
15	7R17585	0.3	0.15	15	35	<5	0.47	2	<1	63	149	0.48	<10	<0.01	56	271	0.03	2	40	18	<5	<20	23	<0.01	<10	<1	<10	5	88
16	7R17586	0.4	0.27	15	50	<5	0.43	<1	2	66	235	0.77	<10	0.04	166	46	0.03	2	100	18	<5	<20	34	<0.01	<10	2	<10	7	59
17	7R17587	<0.2	0.52	10	60	<5	0.59	<1	2	70	116	1.17	<10	0.15	222	24	0.05	3	230	16	<5	<20	33	0.02	<10	8	<10	3	57
18	7R17588	0.8	0.45	10	55	<5	0.54	<1	2	48	93	1.09	<10	0.14	210	22	0.04	3	220	16	<5	<20	35	0.02	<10	7	<10	3	56
19	7R17589	0.5	0.49	20	125	<5	0.38	<1	3	49	339	1.13	<10	0.23	189	225	0.04	2	240	16	<5	<20	25	0.06	<10	11	<10	2	42
20	7R17590	0.5	0.59	10	155	5	0.39	<1	3	56	60	1.27	<10	0.26	206	16	0.05	3	300	18	<5	<20	34	0.06	<10	13	<10	<1	39
21	7R17591	0.4	0.48	20	85	<5	0.98	<1	3	57	261	1.53	<10	0.18	269	70	0.03	3	270	16	5	<20	52	0.02	<10	8	<10	<1	34
22	7R17592	0.2	0.21	10	35	<5	1.46	<1	<1	41	61	0.62	<10	0.03	121	80	0.02	2	70	20	<5	<20	42	<0.01	<10	2	<10	9	55
23	7R17593	0.3	0.35	10	45	<5	0.45	<1	2	60	65	1.03	<10	0.09	158	59	0.05	2	120	16	<5	<20	21	0.02	<10	4	<10	5	28
24	7R17594	0.2	0.49	10	85	<5	0.57	<1	3	49	98	1.46	<10	0.21	229	14	0.04	4	280	16	<5	<20	25	0.04	<10	10	<10	2	50
25	7R17595	0.2	0.32	10	55	<5	0.34	<1	2	51	86	1.05	<10	0.10	149	17	0.04	1	140	16	<5	<20	18	0.03	<10	6	<10	6	46
26	7R17596	<0.2	0.67	5	120	<5	1.31	1	8	18	105	2.67	10	0.47	619	627	0.04	17	880	18	5	<20	124	0.03	<10	33	<10	15	87
27	7R17597	0.2	0.19	15	25	<5	0.52	<1	1	51	50	0.59	<10	0.01	77	31	0.03	1	30	16	<5	<20	23	<0.01	<10	<1	<10	7	25
28	7R17598	<0.2	0.62	20	145	5	0.28	<1	3	66	73	1.38	<10	0.26	218	8	0.06	3	300	18	<5	<20	24	0.08	<10	13	<10	<1	36

Et #.	Tag #	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
QC DATA:																													
<i>Repeat:</i>																													
1	7R17571	0.8	0.46	10	95	<5	0.52	<1	3	46	497	1.45	<10	0.17	173	81	0.03	2	290	14	<5	<20	29	0.05	<10	8	<10	<1	50
10	7R17580	0.2	0.16	10	30	<5	0.29	<1	<1	59	39	0.39	<10	0.01	59	222	0.04	1	40	16	<5	<20	7	<0.01	<10	<1	<10	7	25
19	7R17589	0.8	0.48	15	120	<5	0.38	<1	3	49	339	1.11	<10	0.22	185	226	0.04	2	240	14	<5	<20	21	0.06	<10	11	<10	2	41
<i>Resplit:</i>																													
1	7R17571	0.7	0.46	15	105	<5	0.49	1	3	46	480	1.43	<10	0.21	173	83	0.05	4	310	18	5	<20	31	0.04	<10	10	<10	<1	56
<i>Standard:</i>																													
Pb113		11.8	0.27	40	60	<5	1.65	40	3	6	2268	1.10	<10	0.10	1479	73	0.01	3	80	5586	15	<20	86	0.01	<10	8	<10	<1	6979

JJ/nl
dlr1497S
XLS/07

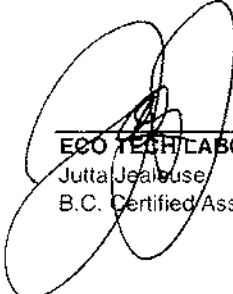

ECO TECH LABORATORY LTD.
Jutta Jealous
B.C. Certified Assayer

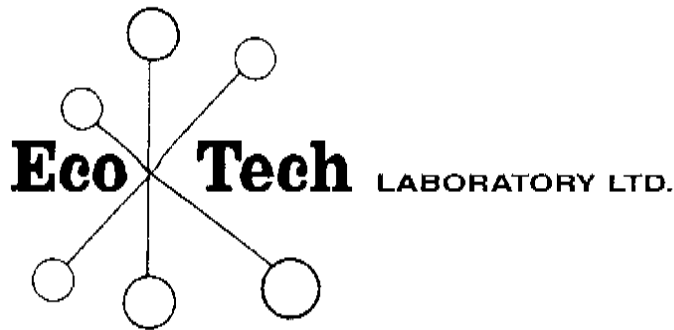

ASSAYING, GEOCHEMISTRY
ANALYTICAL CHEMISTRY
ENVIRONMENTAL TESTING
ISO 9001 Accredited Co.

10041 Dallas Drive, Kamloops, BC V2C 6T4
Phone (250) 573-5700 Fax (250) 573-4557
E-mail: info@ecotechlab.com
www.ecotechlab.com

CERTIFICATE OF ASSAY AK 2007-1364

Pacific Cascade Resources
520 - 700 W. Pender Street
Vancouver, BC
V6C 1G8

27-Sep-07

No. of samples received: 80
Sample Type: Core
Project: Crack Moly

ET #.	Tag #	Mo (%)
1	7R17401	0.320
2	7R17402	0.102
5	7R17405	0.055
11	7R17411	0.064
17	7R17417	0.081
18	7R17418	0.108
25	7R17425	0.064
30	7R17430	0.196
31	7R17431	0.459
32	7R17432	0.239
36	7R17436	0.064
37	7R17437	0.061
38	7R17438	0.061
39	7R17439	0.064
43	7R17443	0.189
44	7R17444	0.097
45	7R17445	0.092
46	7R17446	0.201
47	7R17447	0.083
49	7R17449	0.050
51	7R17451	0.064
55	7R17455	0.058
56	7R17456	0.112
59	7R17459	0.129
60	7R17460	0.082
61	7R17461	0.067
62	7R17462	0.078
64	7R17464	0.231

ECO TECH LABORATORY LTD.

Julia Jealouse
B.C. Certified Assayer
27-Sep-07

Pacific Cascade Resources AK7-1364

ET #.	Tag #	Mo (%)
65	7R17465	0.074
66	7R17466	0.078
67	7R17467	0.064
68	7R17468	0.284
69	7R17469	0.297
76	7R17476	0.099
78	7R17478	0.064
79	7R17479	0.183

QC DATA:

Repeat:

30 7R17430
44 7R17444
55 7R17455


0.193
0.099
0.058

Standard:

MP2
MP2

0.282
0.285

JJ/dc
XLS/07


ECO TECH LABORATORY LTD.
Jutta Jealouse
B.C. Certified Assayer

ECO TECH LABORATORY LTD.

10041 Dallas Drive

KAMLOOPS, B.C.

V2C 6T4

ICP CERTIFICATE OF ANALYSIS AK 2007- 1364

Pacific Cascade Resources

520 - 700 W. Pender Street

Vancouver, BC

V6C 1G8

Phone: 250-573-5700

Fax : 250-573-4557

No. of samples received: 80

Sample Type: Core

Project: Crack Moly

Values in ppm unless otherwise reported

Et #.	Tag #	Ag	Al%	As	Ba	Bi	Ca%	Cd	Co	Cr	Cu	Fe%	K%	La	Mg%	Mn	Mo	Na%	Ni	P	Pb	Sb	Sn	Sr	Ti%	U	V	W	Y	Zn
1	7R17401	<0.2	6.17	5	1100	<5	1.73	<1	2	118	42	2.21	1.85	<10	0.52	584	3113	1.93	9	1020	34	<5	<20	347	0.19	<10	33	<10	17	103
2	7R17402	0.6	5.84	5	1175	<5	0.83	<1	<1	94	40	1.16	2.43	<10	0.15	311	1082	1.48	5	670	42	<5	<20	193	0.06	<10	8	<10	14	89
3	7R17403	<0.2	5.88	15	960	<5	1.42	<1	3	102	67	2.01	1.86	<10	0.37	450	172	1.72	8	420	32	<5	<20	268	0.15	<10	25	<10	13	98
4	7R17404	<0.2	6.00	5	660	<5	1.74	1	4	118	94	2.75	1.36	<10	0.54	557	209	1.88	9	620	30	<5	<20	320	0.20	<10	32	<10	13	163
5	7R17405	<0.2	5.48	<5	525	<5	2.03	<1	2	106	54	1.70	1.20	<10	0.28	444	529	2.31	6	1950	30	<5	<20	405	0.13	<10	18	<10	17	71
6	7R17406	<0.2	4.95	30	840	<5	0.89	<1	1	106	73	1.29	1.85	<10	0.19	342	328	1.59	5	310	30	<5	<20	234	0.08	<10	12	<10	8	91
7	7R17407	<0.2	4.88	10	900	5	0.80	2	1	130	101	1.23	2.15	<10	0.19	284	361	1.45	5	270	30	<5	<20	176	0.07	<10	12	<10	10	118
8	7R17408	<0.2	5.17	5	930	<5	1.07	<1	2	131	121	1.54	2.04	<10	0.25	354	446	1.69	6	340	32	<5	<20	251	0.10	<10	16	<10	12	65
9	7R17409	<0.2	5.15	<5	995	<5	0.89	<1	1	87	35	1.19	2.10	<10	0.16	310	318	1.65	4	310	34	<5	<20	203	0.08	<10	10	<10	11	66
10	7R17410	<0.2	5.54	10	860	<5	1.38	<1	2	96	46	1.38	1.57	<10	0.24	339	252	2.20	6	360	32	<5	<20	408	0.13	<10	13	<10	6	63
11	7R17411	0.2	6.15	10	935	<5	1.59	<1	7	23	124	2.84	2.30	30	0.62	717	631	1.46	20	1000	40	<5	<20	335	0.29	<10	44	<10	15	96
12	7R17412	<0.2	5.59	5	855	<5	1.60	<1	1	89	52	1.22	1.55	<10	0.23	317	76	2.41	5	330	30	<5	<20	411	0.12	<10	14	<10	6	52
13	7R17413	<0.2	5.36	<5	965	<5	0.96	<1	1	89	103	1.30	2.14	10	0.20	300	259	1.78	4	320	32	<5	<20	247	0.09	<10	13	<10	10	77
14	7R17414	0.2	4.68	15	835	<5	0.65	2	2	106	139	1.42	1.80	<10	0.19	279	401	1.50	5	530	24	<5	<20	161	0.08	<10	13	<10	11	134
15	7R17415	0.4	4.61	<5	940	<5	0.85	2	1	89	81	1.09	2.11	<10	0.17	276	59	1.63	4	300	28	<5	<20	216	0.07	<10	11	<10	12	160
16	7R17416	0.2	4.65	<5	495	<5	1.77	<1	<1	111	29	1.38	0.87	<10	0.23	368	400	2.38	6	560	22	<5	<20	431	0.14	<10	15	<10	5	77
17	7R17417	<0.2	5.59	5	1125	<5	1.25	<1	<1	62	34	0.76	2.26	<10	0.09	242	812	2.16	3	1340	34	<5	<20	234	0.05	<10	6	<10	16	48
18	7R17418	0.2	5.26	5	625	<5	1.90	<1	2	89	76	1.88	1.07	<10	0.44	476	1094	2.35	6	600	26	<5	<20	443	0.23	<10	35	<10	5	101
19	7R17419	<0.2	5.82	5	1015	<5	1.76	<1	3	84	78	2.06	1.51	<10	0.42	478	33	2.59	6	600	30	<5	<20	424	0.24	<10	34	<10	7	114
20	7R17420	<0.2	6.33	<5	1015	<5	1.42	<1	3	88	55	1.88	2.41	10	0.37	417	84	1.96	7	420	36	<5	<20	260	0.14	<10	25	<10	15	87
21	7R17421	<0.2	5.54	<5	1055	<5	1.12	<1	2	88	12	1.35	2.28	10	0.26	310	161	1.96	5	310	32	<5	<20	277	0.10	<10	16	<10	12	59
22	7R17422	<0.2	5.80	<5	950	<5	1.36	<1	<1	86	36	1.29	1.95	<10	0.20	274	75	2.39	4	310	30	<5	<20	306	0.11	<10	14	<10	9	52
23	7R17423	<0.2	5.88	<5	1030	<5	1.01	<1	1	76	113	1.18	2.33	10	0.15	270	61	1.97	4	270	34	<5	<20	213	0.08	<10	10	<10	13	48
24	7R17424	0.3	6.13	<5	1290	<5	0.53	1	<1	54	88	0.62	3.19	10	0.06	138	58	1.75	3	190	42	<5	<20	150	0.03	<10	2	<10	11	68
25	7R17425	<0.2	6.72	5	895	<5	1.83	<1	6	20	138	2.73	2.42	30	0.61	692	612	1.52	19	930	36	<5	<20	335	0.27	<10	45	<10	15	95
26	7R17426	<0.2	5.74	5	1280	10	0.56	1	<1	58	41	0.57	2.84	10	0.06	177	355	1.57	3	160	46	<5	<20	165	0.03	<10	2	<10	11	125
27	7R17427	<0.2	5.21	<5	1535	5	0.52	<1	<1	72	23	0.52	2.99	10	0.06	151	483	1.76	3	170	44	<5	<20	203	0.03	<10	3	<10	9	55
28	7R17428	0.2	5.22	10	1470	10	0.50	1	<1	70	49	0.54	3.15	10	0.05	139	230	1.60	2	280	42	<5	<20	174	0.02	<10	3	<10	12	71
29	7R17429	0.3	4.92	<5	1055	5	0.60	5	1	121	119	1.17	2.37	10	0.15	295	164	1.71	4	250	30	<5	<20	174	0.06	<10	10	<10	11	240
30	7R17430	<0.2	4.39	<5	490	<5	0.87	<1	<1	87	69	0.93	1.33	10	0.08	235	2087	2.45	3	230	26	<5	<20	141	0.05	<10	6	<10	7	48

Et #.	Tag #	Ag	Al%	As	Ba	Bi	Ca%	Cd	Co	Cr	Cu	Fe%	K%	La	Mg%	Mn	Mo	Na%	Ni	P	Pb	Sb	Sn	Sr	Ti%	U	V	W	Y	Zn
31	7R17431	<0.2	4.96	5	320	<5	1.75	<1	<1	92	83	1.43	1.12	<10	0.19	404	4706	2.75	5	550	24	<5	<20	319	0.10	<10	13	<10	6	88
32	7R17432	<0.2	4.58	<5	690	<5	0.95	<1	<1	87	39	1.00	1.77	<10	0.12	299	2471	2.12	3	230	24	<5	<20	186	0.06	<10	8	<10	8	47
33	7R17433	<0.2	5.50	<5	1295	5	0.42	<1	<1	98	78	0.75	2.44	10	0.05	167	72	1.98	4	140	32	<5	<20	97	0.03	<10	3	<10	13	29
34	7R17434	0.2	5.48	<5	445	<5	2.26	<1	2	93	38	1.32	0.76	<10	0.26	341	73	2.72	4	400	22	<5	<20	462	0.17	<10	18	<10	2	71
35	7R17435	<0.2	6.21	<5	550	<5	2.30	<1	1	101	39	1.29	0.82	<10	0.26	325	119	2.82	5	380	22	<5	<20	524	0.16	<10	18	<10	2	72
36	7R17436	<0.2	6.39	5	885	<5	1.65	<1	6	22	130	2.81	2.50	30	0.60	667	625	1.57	19	930	36	<5	<20	321	0.26	<10	45	<10	16	99
37	7R17437	3.0	5.78	5	600	20	1.89	2	2	94	1523	1.55	0.93	<10	0.28	312	618	2.69	4	390	32	<5	<20	500	0.16	<10	17	<10	3	129
38	7R17438	<0.2	5.58	<5	540	<5	2.03	<1	1	84	48	1.38	1.03	<10	0.26	338	617	2.59	4	400	26	<5	<20	453	0.16	<10	17	<10	3	68
39	7R17439	<0.2	6.64	10	915	<5	1.65	<1	7	24	128	3.14	2.66	30	0.61	657	634	1.65	21	960	40	<5	<20	340	0.30	<10	45	<10	16	92
40	7R17440	<0.2	6.95	5	1205	<5	1.64	<1	2	38	106	1.71	2.24	<10	0.46	377	173	2.36	4	580	38	<5	<20	586	0.19	<10	26	<10	3	50
41	7R17441	<0.2	5.82	<5	600	<5	1.50	<1	2	141	157	1.54	1.19	<10	0.25	356	422	2.29	5	410	24	<5	<20	428	0.13	<10	16	<10	3	56
42	7R17442	<0.2	6.26	<5	615	<5	1.76	<1	1	135	83	1.46	1.43	<10	0.24	410	493	2.13	6	360	26	<5	<20	367	0.13	<10	17	<10	6	61
43	7R17443	<0.2	6.37	10	1240	5	0.93	<1	<1	158	41	1.27	2.48	10	0.19	366	1939	1.59	6	340	32	<5	<20	298	0.09	<10	13	<10	9	90
44	7R17444	<0.2	5.53	<5	1040	<5	0.72	4	<1	115	105	1.22	2.43	10	0.11	305	1020	1.51	4	290	30	<5	<20	169	0.05	<10	8	<10	13	200
45	7R17445	0.4	6.30	<5	685	<5	1.41	2	<1	116	190	1.46	1.77	<10	0.22	420	956	1.96	4	310	36	<5	<20	375	0.12	<10	14	<10	6	275
46	7R17446	<0.2	7.24	5	1640	5	0.67	<1	<1	100	29	0.54	3.40	20	0.06	154	2069	1.74	3	180	44	<5	<20	237	0.03	<10	3	<10	14	40
47	7R17447	<0.2	6.69	<5	760	<5	1.71	<1	<1	136	32	1.48	1.74	<10	0.21	442	846	2.12	5	590	28	<5	<20	377	0.12	<10	14	<10	7	59
48	7R17448	<0.2	5.45	<5	435	<5	1.90	<1	1	107	55	1.58	0.91	<10	0.28	321	447	2.56	5	450	22	<5	<20	481	0.15	<10	19	<10	4	86
49	7R17449	<0.2	5.67	<5	515	<5	1.72	<1	2	99	43	1.81	1.18	<10	0.30	460	518	2.30	6	530	28	<5	<20	439	0.17	<10	22	<10	5	92
50	7R17450	<0.2	5.60	5	610	<5	1.75	<1	1	101	25	1.68	1.22	<10	0.30	406	428	2.46	5	440	26	<5	<20	458	0.17	<10	22	<10	5	70
51	7R17451	0.2	6.66	10	890	<5	1.52	<1	6	22	126	2.84	2.76	30	0.58	681	636	1.51	19	940	38	<5	<20	318	0.27	<10	46	<10	16	98
52	7R17452	<0.2	5.46	5	605	<5	1.63	<1	2	87	58	1.76	1.23	<10	0.31	390	146	2.41	6	470	24	<5	<20	416	0.18	<10	23	<10	6	70
53	7R17453	<0.2	5.02	<5	510	<5	1.62	<1	1	105	47	1.49	1.02	<10	0.28	334	432	2.58	5	420	24	<5	<20	459	0.15	<10	18	<10	4	51
54	7R17454	<0.2	5.51	<5	510	<5	1.77	<1	2	92	33	1.57	0.98	<10	0.29	392	52	2.46	5	440	24	<5	<20	472	0.16	<10	21	<10	5	55
55	7R17455	<0.2	5.77	<5	570	<5	1.87	<1	1	100	29	1.60	1.24	<10	0.25	363	607	2.34	5	1010	24	<5	<20	419	0.17	<10	21	<10	10	60
56	7R17456	<0.2	5.64	5	820	<5	1.24	<1	<1	99	36	1.19	1.78	<10	0.16	311	1167	2.45	4	630	30	<5	<20	329	0.09	<10	11	<10	13	93
57	7R17457	<0.2	4.95	<5	1010	<5	0.53	1	<1	120	53	0.91	2.41	10	0.09	198	177	1.85	4	230	32	<5	<20	147	0.04	<10	6	<10	12	72
58	7R17458	<0.2	5.16	<5	905	<5	1.01	<1	<1	122	56	1.35	2.06	<10	0.17	342	174	2.20	5	320	32	<5	<20	263	0.09	<10	12	<10	9	74
59	7R17459	<0.2	4.98	<5	765	<5	1.08	<1	<1	112	92	1.19	2.14	<10	0.16	291	1319	2.24	4	350	26	<5	<20	267	0.08	<10	13	<10	10	72
60	7R17460	<0.2	5.00	<5	865	10	0.97	14	<1	121	83	1.40	1.89	<10	0.19	263	785	2.02	4	290	26	<5	<20	296	0.10	<10	12	<10	8	514
61	7R17461	<0.2	4.57	<5	650	<5	1.26	3	<1	130	19	1.35	1.37	<10	0.20	245	692	2.05	5	340	22	<5	<20	319	0.12	<10	15	<10	7	173
62	7R17462	<0.2	4.55	<5	760	<5	1.12	<1	<1	108	39	1.36	1.57	<10	0.24	275	780	2.07	5	360	24	<5	<20	367	0.11	<10	17	<10	7	70
63	7R17463	<0.2	5.66	5	640	<5	1.46	4	1	102	50	1.79	1.30	<10	0.25	378	416	2.30	5	440	28	<5	<20	409	0.14	<10	17	<10	5	200
64	7R17464	<0.2	4.79	5	545	<5	1.41	3	<1	123	62	1.75	1.21	<10	0.30	404	2417	2.24	6	470	24	<5	<20	404	0.16	<10	22	<10	5	157
65	7R17465	<0.2	4.79	10	760	<5	1.07	<1	<1	116	38	1.47	1.64	<10	0.26	336	759	1.97	5	410	26	<5	<20	325	0.13	<10	20	<10	8	63
66	7R17466	<0.2	4.90	5	635	<5	1.55	<1	<1	90	59	1.63	1.33	<10	0.26	375	787	2.41	5	430	22	<5	<20	408	0.15	<10	20	<10	5	54
67	7R17467	0.2	6.52	10	885	<5	1.55	<1	6	22	127	2.94	2.79	30	0.58	673	616	1.53	19	930	36	<5	<20	327	0.27	<10	45	<10	16	90
68	7R17468	<0.2	4.98	5	1050	<5	0.88	<1	<1	104	58	1.03	2.60	<10	0.11	240	2888	1.90	4	290	30	<5	<20	192	0.06	<10	8	<10	10	28
69	7R17469	<0.2	5.32	10	1270	5	0.78	1	<1	135	110	1.20	2.79	10	0.13	241	3085	1.89	5	370	34	<5	<20	250	0.06	<10	8	<10	10	76
70	7R17470	<0.2	4.87	<5	1070	<5	0.57	<1	<1	109	61	0.92	2.81	<10	0.08	263	29	2.18	4	170	34	<5	<20	143	0.04	<10	7	<10	13	30

Et #.	Tag #	Ag	Al%	As	Ba	Bi	Ca%	Cd	Co	Cr	Cu	Fe%	K%	La	Mg%	Mn	Mo	Na%	Ni	P	Pb	Sb	Sn	Sr	Ti%	U	V	W	Y	Zn
71	7R174-71	<0.2	7.17	5	995	<5	2.28	<1	2	32	162	1.96	2.49	<10	0.42	442	217	2.70	3	720	36	<5	<20	542	0.21	<10	27	<10	3	45
72	7R174-72	<0.2	4.71	<5	720	<5	1.21	<1	1	89	87	1.65	1.81	<10	0.23	385	288	2.23	5	370	24	<5	<20	318	0.13	<10	21	<10	7	62
73	7R174-73	<0.2	4.74	5	1590	5	0.48	2	<1	112	121	0.96	2.75	10	0.07	161	234	1.47	4	200	36	<5	<20	151	0.04	<10	6	<10	9	132
74	7R174-74	<0.2	4.82	<5	920	<5	0.99	<1	<1	98	87	1.17	2.34	<10	0.14	333	87	1.98	4	270	28	<5	<20	239	0.07	<10	11	<10	6	30
75	7R174-75	<0.2	4.84	240	1085	10	0.36	3	1	133	84	1.28	2.64	<10	0.09	180	462	1.37	6	290	30	<5	<20	137	0.05	<10	10	<10	7	61
76	7R174-76	<0.2	5.16	15	930	<5	1.18	<1	<1	92	47	1.42	2.13	<10	0.14	303	1053	2.18	5	390	26	<5	<20	273	0.11	<10	13	<10	6	50
77	7R174-77	<0.2	4.60	25	1035	<5	0.39	<1	<1	97	77	0.99	2.34	<10	0.11	166	245	1.97	4	250	24	<5	<20	209	0.08	<10	12	<10	6	50
78	7R174-78	<0.2	6.51	10	885	<5	1.52	<1	6	20	132	2.98	2.58	30	0.59	678	622	1.67	19	960	36	<5	<20	331	0.28	<10	49	<10	16	91
79	7R174-79	<0.2	4.22	10	800	<5	0.84	<1	<1	76	44	1.22	1.77	<10	0.19	287	1776	2.25	4	320	22	<5	<20	311	0.11	<10	16	<10	5	35
80	7R174-80	<0.2	5.51	20	695	<5	1.04	<1	1	53	47	1.65	2.01	20	0.23	581	36	1.85	4	390	28	<5	<20	210	0.12	<10	9	<10	13	25

QC DATA:

Repeat:

1	7R174-01	<0.2	6.03	5	1065	<5	1.69	<1	2	118	41	2.24	1.81	<10	0.50	574	3141	2.00	9	1010	32	<5	<20	336	0.19	<10	33	<10	17	105
10	7R174-10	<0.2	5.45	15	830	<5	1.44	<1	1	89	47	1.32	1.61	<10	0.22	327	253	2.32	5	330	28	<5	<20	384	0.12	<10	13	<10	6	61
19	7R174-19	0.2	5.75	<5	965	<5	1.72	<1	2	78	79	1.97	1.55	<10	0.41	453	32	2.45	6	570	26	<5	<20	427	0.21	<10	35	<10	7	110
37	7R174-37	3.0	5.80	5	590	20	1.87	2	2	93	1572	1.59	0.90	<10	0.28	318	620	2.60	4	410	32	<5	<20	502	0.16	<10	16	<10	2	130
45	7R174-45	0.3	6.15	<5	680	<5	1.38	3	<1	111	184	1.54	1.72	<10	0.22	431	982	2.03	5	330	38	<5	<20	367	0.12	<10	13	<10	6	287
54	7R174-54	<0.2	5.67	5	515	<5	1.77	<1	2	86	35	1.61	1.05	<10	0.31	403	63	2.48	6	460	26	<5	<20	477	0.17	<10	22	<10	5	58
71	7R174-71	<0.2	7.25	10	975	<5	2.15	<1	2	31	163	2.09	2.69	<10	0.44	460	221	2.98	5	730	38	<5	<20	537	0.23	<10	28	<10	3	48
80	7R174-80	<0.2	5.62	20	670	5	1.07	<1	1	53	49	1.73	2.03	20	0.22	602	40	1.95	4	410	28	5	<20	200	0.13	<10	8	<10	13	28


Resplit:


1	7R174-01	<0.2	5.84	5	1060	<5	1.71	<1	3	118	40	2.13	1.88	<10	0.53	545	3264	2.10	7	940	28	<5	<20	349	0.18	<10	36	<10	16	98
37	7R174-37	2.6	5.85	5	645	20	1.84	<1	2	95	1527	1.46	1.01	<10	0.30	335	617	2.81	5	410	30	<5	<20	508	0.16	<10	18	<10	3	111
72	7R174-72	<0.2	4.67	<5	735	<5	1.17	<1	1	90	87	1.53	1.91	<10	0.23	373	309	2.30	4	370	26	<5	<20	306	0.13	<10	20	<10	7	60

Standard:

STSD3		0.5	5.63	25	1350	<5	2.48	1	18	65	41	4.27	1.28	30	1.35	2548	8	1.01	35	1700	50	<5	<20	263	0.32	<10	121	<10	33	209
STSD3		0.4	5.78	25	1410	<5	2.37	1	17	63	41	4.32	1.33	30	1.31	2527	7	1.06	33	1680	52	<5	<20	263	0.34	<10	114	<10	33	201
STSD3		0.4	5.70	25	1395	<5	2.45	<1	17	61	42	4.32	1.39	30	1.29	2540	7	1.07	31	1650	51	5	<20	260	0.34	<10	117	<10	32	204

ICP: 4-Acid Digestion/ ICP-Finish
 Ag: 4- Acid Digestion/ AA-Finish

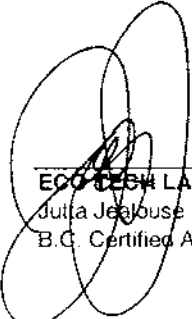
 ECO TECH LABORATORY LTD.
 Julia Jealous
 B.C. Certified Assayer

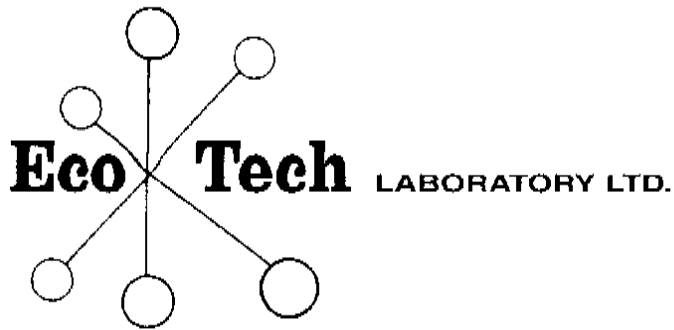

ASSAYING, GEOCHEMISTRY
ANALYTICAL CHEMISTRY
ENVIRONMENTAL TESTING
ISO 9001 Accredited Co.

10041 Dallas Drive, Kamloops, BC V2C 6T4
Phone (250) 573-5700 Fax (250) 573-4557
E-mail: info@ecotechlab.com
www.ecotechlab.com

CERTIFICATE OF ASSAY AK 2007-1361

Pacific Cascade Resources
520 - 700 W. Pender Street
Vancouver, BC
V6C 1G8

27-Sep-07

No. of samples received: 90
Sample Type: Core
Project: Crack Moly

ET #.	Tag #	Mo (%)
1	7R17481	0.064
3	7R17483	0.075
15	7R17495	0.063
21	7R17501	0.069
25	7R17505	0.049
28	7R17508	3.320
30	7R17510	0.063
31	7R17511	0.988
34	7R17514	0.314
35	7R17515	0.122
36	7R17516	0.064
37	7R17517	0.049
40	7R17520	0.064
44	7R17524	0.318
49	7R17529	0.073
50	7R17530	0.063
59	7R17539	0.064
68	7R17548	0.209
71	7R17551	0.062
77	7R17557	0.050
78	7R17558	0.053
81	7R17561	0.063
85	7R17565	0.050

QC DATA:

Repeat:


28	7R17508	3.324
34	7R17514	0.318
59	7R17539	0.060

ECOTECH LABORATORY LTD.
Jutta Jealouse
B.C. Certified Assayer

Pacific Cascade Resources AK7 - 1361

ET #.	Tag #	Mo (%)
Standard:		
MP2		0.281
MP2		0.278

JJ/dc
XLS/07

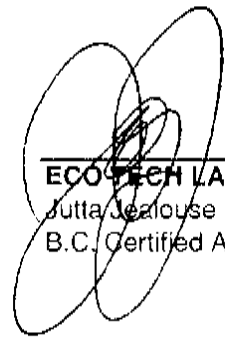

Eco Tech LABORATORY LTD.
Jutta Jealous
B.C. Certified Assayer

ECO TECH LABORATORY LTD.

10041 Dallas Drive

KAMLOOPS, B.C.

V2C 6T4

ICP CERTIFICATE OF ANALYSIS AK 2007- 1361

Pacific Cascade Resources

520 - 700 W. Pender Street

Vancouver, BC

V6C 1G8

Phone: 250-573-5700

Fax : 250-573-4557

No. of samples received: 90

Sample Type: Core

Project: Crack Moly

Values in ppm unless otherwise reported

Et #.	Tag #	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	K %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
1	7R17481	0.2	6.55	5	800	<5	2.67	<1	6	21	133	2.68	2.59	30	0.54	520	625	1.50	14	830	34	<5	<20	324	0.22	<10	45	<10	13	87
2	7R17482	<0.2	6.92	5	985	<5	2.04	<1	<1	51	33	1.01	2.37	<10	0.14	204	88	2.15	3	280	30	<5	<20	275	0.07	<10	11	<10	7	38
3	7R17483	<0.2	6.59	<5	810	<5	2.36	<1	1	86	21	1.40	1.88	<10	0.23	249	759	2.04	4	350	26	<5	<20	368	0.11	<10	16	<10	8	60
4	7R17484	<0.2	6.57	<5	655	<5	3.02	<1	2	74	15	1.69	1.46	<10	0.31	277	206	2.33	5	470	26	<5	<20	471	0.16	<10	26	10	6	65
5	7R17485	<0.2	7.19	<5	800	<5	2.63	<1	1	71	44	1.45	1.77	<10	0.22	271	179	2.17	4	380	30	<5	<20	403	0.12	<10	16	10	8	85
6	7R17486	<0.2	5.63	<5	755	<5	2.03	1	1	77	54	1.41	1.84	<10	0.21	251	225	2.19	4	340	28	<5	<20	367	0.11	<10	16	<10	8	95
7	7R17487	<0.2	6.20	<5	745	<5	2.67	4	2	69	78	1.58	1.77	<10	0.27	235	426	2.07	3	390	28	<5	<20	421	0.14	<10	22	<10	7	159
8	7R17488	<0.2	5.87	<5	835	5	2.04	4	1	81	60	1.56	2.02	10	0.20	275	210	2.08	4	320	28	<5	<20	345	0.11	<10	17	<10	9	169
9	7R17489	<0.2	5.65	<5	1070	<5	1.25	<1	<1	49	51	1.03	2.63	10	0.12	191	98	1.89	2	190	30	<5	<20	249	0.06	<10	8	<10	11	32
10	7R17490	<0.2	5.84	<5	1170	5	1.03	<1	<1	54	83	0.80	2.90	10	0.06	104	155	1.58	2	180	34	<5	<20	142	0.03	<10	4	<10	8	59
11	7R17491	<0.2	6.85	5	1270	<5	0.92	<1	<1	55	55	0.54	3.10	20	0.05	91	323	1.39	2	150	34	<5	<20	153	0.02	<10	2	<10	6	19
12	7R17492	0.2	6.75	5	1200	<5	1.06	<1	<1	83	68	0.96	3.02	10	0.07	119	82	1.69	3	160	34	<5	<20	145	0.03	<10	4	<10	6	16
13	7R17493	0.2	6.14	10	1080	<5	1.01	<1	<1	80	51	0.93	3.09	20	0.09	137	161	1.31	1	220	38	<5	<20	149	0.04	<10	3	<10	7	22
14	7R17494	<0.2	8.08	10	1210	<5	1.10	<1	<1	77	66	0.81	3.14	10	0.06	103	258	1.57	2	180	44	<5	<20	155	0.02	<10	3	<10	7	23
15	7R17495	<0.2	6.59	5	840	<5	2.64	<1	6	20	139	3.01	2.39	30	0.57	585	628	1.64	17	940	38	<5	<20	360	0.26	<10	45	<10	16	93
16	7R17496	<0.2	6.79	15	1265	<5	1.21	<1	<1	64	40	0.86	2.97	20	0.07	214	24	1.93	2	180	36	<5	<20	174	0.03	<10	2	<10	8	56
17	7R17497	<0.2	6.07	45	1075	<5	0.78	<1	<1	57	48	0.90	2.96	20	0.07	166	164	2.03	2	190	36	<5	<20	124	0.03	<10	3	<10	9	23
18	7R17498	<0.2	7.19	5	725	<5	2.87	2	2	46	110	1.89	1.80	10	0.35	335	213	2.38	4	560	30	<5	<20	528	0.17	<10	29	<10	7	113
19	7R17499	1.0	7.27	5	610	<5	3.97	<1	2	124	33	1.70	0.91	<10	0.41	310	13	2.72	7	580	28	<5	<20	665	0.21	<10	33	<10	4	53
20	7R17500	0.2	7.32	<5	880	<5	2.93	<1	2	68	145	1.64	2.04	<10	0.27	294	123	2.39	4	540	32	<5	<20	521	0.14	<10	22	<10	8	51
21	7R17501	<0.2	6.73	10	725	<5	3.00	<1	2	93	77	1.75	1.60	<10	0.30	381	700	2.28	5	810	32	<5	<20	469	0.15	<10	22	<10	14	45
22	7R17502	<0.2	6.23	5	1200	<5	1.43	<1	<1	54	73	1.03	2.71	10	0.13	218	234	1.85	2	220	38	<5	<20	244	0.06	<10	9	<10	14	31
23	7R17503	<0.2	6.84	5	1055	<5	2.20	<1	1	53	62	1.24	2.24	<10	0.20	278	74	2.21	4	290	34	<5	<20	367	0.10	<10	14	<10	11	42
24	7R17504	<0.2	6.91	<5	790	<5	2.42	<1	1	60	68	1.78	2.04	20	0.23	314	147	2.16	4	360	38	<5	<20	396	0.13	<10	18	<10	11	112
25	7R17505	0.2	5.62	<5	1020	<5	1.31	<1	<1	59	84	1.11	2.62	10	0.11	181	510	1.94	3	190	32	<5	<20	227	0.06	<10	9	<10	11	35
26	7R17506	<0.2	6.56	5	900	<5	2.11	<1	<1	55	82	1.21	2.15	10	0.18	255	386	1.98	4	280	32	<5	<20	307	0.08	<10	14	<10	7	45
27	7R17507	<0.2	5.77	<5	475	<5	3.16	<1	1	83	95	1.58	0.96	<10	0.29	292	257	2.13	4	640	24	<5	<20	448	0.14	<10	25	<10	6	51
28	7R17508	<0.2	5.48	35	155	<5	2.46	<1	<1	104	93	1.94	1.12	<10	0.75	447	>10000	2.08	4	840	20	<5	<20	366	0.15	<10	22	<10	8	71
29	7R17509	<0.2	6.72	<5	660	<5	3.12	<1	1	98	19	1.28	0.80	<10	0.28	232	140	2.59	4	360	26	<5	<20	637	0.15	<10	16	<10	2	43
30	7R17510	<0.2	6.37	5	875	<5	2.64	<1	6	21	134	2.98	2.39	30	0.55	612	623	1.67	16	910	36	<5	<20	339	0.26	<10	44	<10	16	99

Et #.	Tag #	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	K %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
31	7R1751 1	0.8	5.83	15	515	<5	2.53	<1	1	100	533	2.03	1.56	<10	0.39	387	9896	2.46	5	480	28	<5	<20	367	0.13	<10	22	<10	6	79
32	7R1751 2	1.2	7.21	15	890	50	2.57	<1	2	77	198	1.78	2.34	10	0.23	318	476	2.18	5	350	52	<5	<20	382	0.10	<10	18	<10	9	52
33	7R1751 3	<0.2	6.14	5	1325	<5	0.81	<1	<1	70	41	0.66	3.16	20	0.06	146	218	1.60	3	190	40	<5	<20	186	0.02	<10	4	<10	8	33
34	7R1751 4	0.2	6.27	10	965	5	1.22	<1	<1	97	100	0.97	2.59	10	0.14	214	3242	1.86	3	220	40	<5	<20	237	0.04	<10	9	<10	8	106
35	7R1751 5	<0.2	5.18	15	1185	10	0.95	<1	<1	86	36	0.80	3.02	10	0.09	153	1226	1.43	3	180	34	<5	<20	179	0.03	<10	6	<10	9	25
36	7R1751 6	<0.2	5.46	5	1355	<5	0.90	<1	<1	101	41	0.92	2.85	10	0.10	194	651	1.49	4	180	34	<5	<20	210	0.04	<10	8	<10	11	37
37	7R1751 7	0.2	5.69	5	1155	<5	1.21	<1	<1	95	64	1.19	2.56	10	0.12	252	505	1.72	4	240	34	<5	<20	221	0.06	<10	10	<10	9	44
38	7R1751 8	0.2	6.04	25	1280	<5	1.04	<1	<1	90	33	1.08	2.79	10	0.09	237	168	1.88	3	210	38	<5	<20	181	0.05	<10	6	<10	13	40
39	7R1751 9	<0.2	5.82	15	875	<5	1.28	<1	1	74	38	1.09	2.32	10	0.14	225	93	2.12	3	280	34	<5	<20	264	0.08	<10	12	<10	12	41
40	7R1752 0	<0.2	6.27	10	860	<5	1.96	<1	5	21	130	2.65	2.55	30	0.55	560	624	1.51	16	830	32	<5	<20	332	0.23	<10	45	<10	15	91
41	7R1752 1	<0.2	5.94	10	665	<5	2.08	<1	1	89	94	1.68	1.66	<10	0.27	378	329	2.30	5	500	30	<5	<20	417	0.15	<10	24	<10	7	56
42	7R1752 2	<0.2	6.70	5	585	<5	2.96	<1	2	74	44	1.99	1.22	<10	0.34	469	110	2.62	5	580	30	<5	<20	528	0.19	<10	30	<10	5	83
43	7R1752 3	<0.2	7.07	5	455	<5	3.22	<1	2	77	89	2.29	1.04	<10	0.38	583	117	2.65	7	670	32	<5	<20	552	0.21	<10	33	<10	3	95
44	7R1752 4	1.3	6.22	50	440	10	1.68	1	2	119	741	2.70	1.86	<10	0.30	372	3277	1.58	6	600	32	<5	<20	291	0.13	<10	46	<10	5	74
45	7R1752 5	0.2	7.11	5	490	<5	2.34	<1	1	80	22	1.29	0.81	<10	0.29	251	23	2.69	4	470	28	<5	<20	640	0.15	<10	16	<10	2	37
46	7R1752 6	0.3	5.48	50	945	<5	0.99	<1	1	112	183	1.24	2.62	10	0.10	186	460	1.53	5	210	32	<5	<20	169	0.05	<10	10	<10	7	28
47	7R1752 7	1.3	5.34	40	870	75	1.02	<1	<1	87	121	1.10	2.44	10	0.10	212	471	1.27	3	190	58	10	<20	154	0.04	<10	13	<10	6	55
48	7R1752 8	<0.2	6.01	5	1045	<5	1.46	<1	<1	90	39	1.27	2.12	10	0.14	336	366	2.07	4	190	32	<5	<20	282	0.07	<10	10	<10	13	52
49	7R1752 9	0.4	5.19	70	855	10	0.68	2	<1	101	106	1.16	2.61	10	0.08	185	759	1.11	4	190	36	5	<20	98	0.03	<10	5	<10	7	83
50	7R1753 0	<0.2	6.76	5	845	<5	1.92	<1	6	20	133	2.77	1.99	30	0.56	591	627	1.57	17	900	34	<5	<20	344	0.24	<10	46	<10	16	93
51	7R1753 1	0.8	5.03	70	660	10	0.46	3	1	62	256	1.40	2.67	10	0.13	197	440	0.64	3	220	32	5	20	69	0.03	<10	9	<10	6	223
52	7R1753 2	<0.2	6.71	35	1165	5	1.05	<1	<1	37	43	0.94	3.10	10	0.09	240	23	1.90	2	210	40	<5	<20	159	0.03	<10	6	<10	9	26
53	7R1753 3	<0.2	6.43	15	1100	<5	1.32	<1	1	72	65	1.29	2.32	10	0.16	358	318	1.89	4	500	36	<5	<20	257	0.08	<10	11	<10	13	50
54	7R1753 4	0.4	6.59	10	1315	<5	0.85	<1	<1	72	66	1.02	2.96	10	0.08	251	196	2.02	3	210	42	<5	<20	150	0.04	<10	5	<10	14	34
55	7R1753 5	0.2	6.52	5	1230	<5	1.11	<1	<1	67	61	0.99	2.94	10	0.09	276	250	2.00	3	190	40	<5	<20	174	0.04	<10	5	<10	13	57
56	7R1753 6	<0.2	6.72	10	1275	<5	0.78	3	<1	54	50	0.81	3.16	20	0.08	193	27	1.58	2	210	44	<5	<20	156	0.03	<10	4	<10	11	225
57	7R1753 7	<0.2	6.21	5	1080	<5	0.98	<1	<1	59	108	1.08	2.82	10	0.10	248	91	1.70	3	270	38	<5	<20	132	0.04	<10	6	<10	11	64
58	7R1753 8	<0.2	6.30	10	1145	<5	0.93	<1	<1	61	304	0.99	2.82	10	0.10	255	197	1.77	3	210	40	<5	<20	138	0.04	<10	6	<10	12	44
59	7R1753 9	<0.2	7.07	10	880	<5	2.05	<1	6	22	131	2.86	2.17	30	0.59	660	634	1.64	17	910	36	<5	<20	335	0.25	<10	45	<10	15	93
60	7R1754 0	<0.2	6.61	5	545	<5	2.47	<1	1	86	14	1.32	0.76	<10	0.30	275	17	2.80	4	450	28	<5	<20	603	0.15	<10	16	<10	2	38
61	7R1754 1	<0.2	4.90	5	890	<5	0.74	<1	<1	83	23	0.78	2.34	10	0.08	187	195	1.42	3	210	34	<5	<20	106	0.03	<10	4	<10	10	50
62	7R1754 2	<0.2	6.03	5	1125	<5	0.83	<1	<1	66	86	0.97	2.77	10	0.09	254	78	1.88	3	280	38	<5	<20	136	0.03	<10	4	<10	13	35
63	7R1754 3	<0.2	5.59	20	1075	<5	0.77	2	<1	79	94	1.07	2.89	10	0.09	186	228	1.68	3	220	36	<5	<20	114	0.03	<10	5	<10	7	73
64	7R1754 4	0.6	6.26	45	1090	<5	0.49	<1	<1	58	387	0.99	2.58	10	0.07	127	163	1.68	3	200	40	<5	<20	98	0.03	<10	5	<10	6	37
65	7R1754 5	<0.2	5.19	10	1255	<5	0.52	<1	<1	47	36	0.77	2.28	20	0.06	192	129	1.91	2	160	42	<5	<20	126	0.03	<10	5	<10	11	46
66	7R1754 6	<0.2	5.72	10	1090	<5	0.68	<1	<1	83	101	1.01	2.61	10	0.06	187	350	1.76	3	200	50	<5	<20	108	0.03	<10	5	<10	9	72
67	7R1754 7	<0.2	6.07	5	1295	<5	0.76	4	<1	64	125	1.02	2.30	10	0.06	197	318	1.65	2	360	50	<5	<20	170	0.03	<10	4	<10	12	287
68	7R1754 8	<0.2	5.66	5	1245	<5	0.59	<1	<1	79	61	0.79	2.63	10	0.05	149	2135	1.56	3	200	52	<5	<20	158	0.02	<10	3	<10	11	80
69	7R1754 9	0.2	5.58	20	1010	<5	0.92	2	1	77	160	1.07	2.39	10	0.13	238	69	1.51	3	300	36	<5	<20	191	0.08	<10	14	<10	8	173
70	7R1755 0	<0.2	6.91	5	710	<5	3.07	<1	2	85	28	1.55	0.94	<10	0.40	396	457	2.69	7	570	38	<5	<20	574	0.22	<10	32	<10	4	112

Et #.	Tag #	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	K %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
71	7R17551	<0.2	6.76	5	860	<5	1.93	<1	6	19	129	2.72	2.13	30	0.57	611	616	1.70	16	860	50	<5	<20	333	0.25	<10	46	<10	16	91
72	7R17552	<0.2	6.53	10	680	<5	2.60	<1	2	90	109	1.35	1.33	<10	0.30	377	400	1.94	6	480	38	<5	<20	449	0.18	<10	31	<10	4	77
73	7R17553	<0.2	5.49	10	445	<5	2.45	<1	2	30	64	1.59	0.91	<10	0.30	383	42	2.19	4	530	34	<5	<20	408	0.20	<10	31	<10	4	71
74	7R17554	<0.2	6.21	115	465	<5	2.18	1	2	83	239	1.93	1.23	<10	0.32	369	87	2.15	6	530	40	10	<20	388	0.19	<10	32	<10	4	73
75	7R17555	<0.2	7.08	15	735	<5	2.76	<1	3	69	134	1.86	1.44	<10	0.34	401	90	2.09	6	490	44	<5	<20	451	0.17	<10	26	<10	6	85
76	7R17556	<0.2	6.61	10	555	<5	2.99	<1	2	70	47	1.52	0.83	<10	0.39	375	218	2.68	6	520	40	<5	<20	576	0.20	<10	33	<10	3	63
77	7R17557	0.4	5.81	45	430	<5	2.24	<1	2	116	311	1.57	1.40	<10	0.28	314	492	1.72	5	430	40	<5	<20	372	0.14	<10	30	<10	4	55
78	7R17558	0.2	5.86	10	570	<5	2.37	<1	2	70	210	1.66	1.28	<10	0.30	317	544	2.37	5	510	38	<5	<20	400	0.17	<10	30	<10	4	59
79	7R17559	<0.2	6.36	10	565	<5	3.09	<1	2	94	37	1.55	0.96	<10	0.35	342	103	2.44	6	560	28	<5	<20	531	0.20	<10	32	<10	3	76
80	7R17560	1.2	5.82	175	550	<5	2.22	4	2	78	122	1.46	1.61	<10	0.30	419	58	2.42	5	410	30	<5	<20	284	0.13	<10	23	<10	7	139
81	7R17561	<0.2	7.14	10	840	<5	2.26	<1	6	20	126	2.95	2.35	30	0.56	659	621	1.65	18	940	42	<5	<20	318	0.27	<10	45	<10	15	101
82	7R17562	<0.2	6.65	30	580	<5	2.66	<1	2	78	31	1.46	0.88	<10	0.36	395	126	2.68	5	540	32	<5	<20	551	0.19	<10	31	<10	3	78
83	7R17563	<0.2	5.95	25	575	<5	1.75	<1	2	68	285	2.26	1.61	<10	0.32	456	23	1.98	5	520	28	<5	<20	390	0.16	<10	29	<10	5	92
84	7R17564	<0.2	6.31	25	665	<5	3.17	<1	2	73	119	1.43	1.48	<10	0.24	368	24	2.39	5	480	34	<5	<20	449	0.18	<10	28	<10	5	87
85	7R17565	<0.2	6.28	5	665	<5	2.67	<1	2	61	24	1.41	0.93	<10	0.36	327	514	2.71	5	500	30	<5	<20	506	0.20	<10	33	<10	4	53
86	7R17566	0.2	5.89	15	580	<5	2.58	<1	2	97	337	1.66	1.37	<10	0.26	381	363	1.99	5	440	34	<5	<20	364	0.15	<10	26	<10	5	68
87	7R17567	<0.2	5.71	10	955	<5	1.54	2	1	62	33	1.03	1.97	<10	0.17	204	175	2.22	3	330	36	<5	<20	304	0.09	<10	16	<10	10	122
88	7R17568	<0.2	5.53	5	495	<5	2.56	<1	1	89	63	1.37	0.92	<10	0.33	410	440	2.70	6	460	32	<5	<20	481	0.18	<10	30	<10	4	63
89	7R17569	<0.2	5.94	5	685	<5	2.64	<1	1	54	31	1.40	1.11	<10	0.34	353	13	2.58	4	480	32	<5	<20	499	0.19	<10	30	<10	5	76
90	7R17570	<0.2	6.05	<5	850	<5	2.08	<1	1	71	35	1.37	1.42	<10	0.34	356	9	2.66	5	450	34	<5	<20	431	0.17	<10	26	<10	6	68

QC DATA:

Repeat:


2	7R17482	<0.2	7.04	5	985	<5	2.05	<1	<1	52	31	1.03	2.41	10	0.14	204	83	2.11	3	290	30	<5	<20	285	0.07	<10	10	<10	7	38
10	7R17490	1.0	6.02	5	1210	<5	1.05	<1	<1	57	84	0.84	2.89	10	0.06	103	154	1.62	3	190	36	<5	<20	150	0.03	<10	5	<10	8	54
19	7R17499	1.1	7.32	5	605	<5	4.11	<1	2	126	33	1.69	0.87	<10	0.39	311	13	2.78	6	570	28	<5	<20	652	0.21	<10	35	<10	4	52
36	7R17516	0.2	5.48	10	1410	<5	0.93	<1	1	103	40	0.94	2.92	10	0.10	201	626	1.55	3	190	38	<5	<20	218	0.05	<10	8	<10	11	42
45	7R17525	1.2	7.35	5	510	<5	2.40	<1	<1	81	23	1.36	0.79	<10	0.30	257	23	2.75	5	480	30	<5	<20	660	0.16	<10	16	<10	3	38
54	7R17534	0.5	6.38	10	1310	<5	0.83	<1	<1	69	66	0.97	2.92	10	0.07	253	185	1.96	3	195	44	<5	<20	145	0.03	<10	5	<10	13	31
72	7R17552	1.0	6.48	10	665	<5	2.49	<1	2	92	111	1.39	1.30	<10	0.30	374	405	1.96	5	500	38	<5	<20	449	0.18	<10	31	<10	4	80
80	7R17560	1.1	5.67	170	525	<5	2.14	4	2	76	123	1.41	1.58	<10	0.30	402	56	2.39	5	400	32	<5	<20	271	0.13	<10	24	<10	7	138
89	7R17569	1.2	6.00	5	695	<5	2.73	<1	2	55	32	1.47	1.13	<10	0.35	365	13	2.49	5	490	32	<5	<20	520	0.19	<10	31	<10	5	79

Resplit:

2	7R17482	<0.2	6.49	5	985	<5	2.10	<1	1	56	29	1.07	1.78	<10	0.13	296	89	2.18	6	240	36	<5	<20	278	0.15	<10	10	<10	9	62
36	7R17516	<0.2	5.57	10	1360	<5	0.90	<1	<1	97	42	0.92	2.92	10	0.09	203	641	1.60	3	180	38	<5	<20	204	0.05	<10	8	<10	11	36
72	7R17552	<0.2	6.30	15	705	<5	2.54	<1	2	92	95	1.38	1.28	<10	0.32	400	400	1.90	5	520	36	<5	<20	446	0.19	<10	30	<10	4	76

Standard:

STD3		0.4	5.97	25	1370	<5	2.91	1	18	63	41	4.46	1.43	40	1.37	2724	6	1.12	31	1740	44	<5	<20	225	0.35	<10	118	<10	34	205
STD3		0.5	5.95	25	1315	<5	2.82	1	16	60	40	4.38	1.32	40	1.34	2658	7	1.11	32	1710	46	<5	<20	234	0.34	<10	122	<10	30	210
STD3		0.4	5.76	25	1395	<5	2.77	1	17	66	42	4.31	1.39	45	1.29	2726	6	1.09	31	1650	46	<5	<20	225	0.34	<10	117	<10	31	202

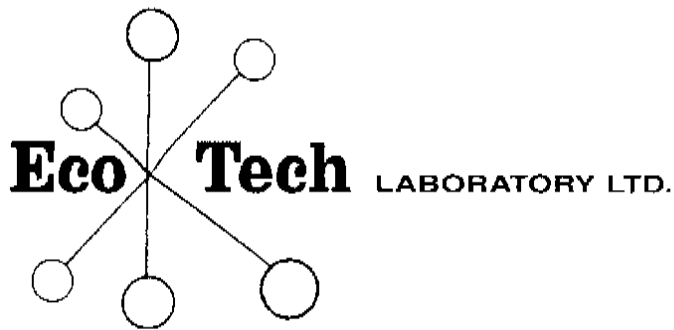

ASSAYING, GEOCHEMISTRY
ANALYTICAL CHEMISTRY
ENVIRONMENTAL TESTING
ISO 9001 Accredited Co.

10041 Dallas Drive, Kamloops, BC V2C 6T4
Phone (250) 573-5700 Fax (250) 573-4557
E-mail: info@ecotechlab.com
www.ecotechlab.com

CERTIFICATE OF ASSAY AK 2007-1317

Pacific Cascade Resources
520 - 700 W. Pender Street
Vancouver, BC
V6C 1G8

14-Sep-07

No. of samples received: 90
Sample Type: Core
Project: Crack Moly
Shipment #: 3
Submitted by: Pacific Cascade Resources

ET #.	Tag #	Mo (%)
9	G082280	0.064
20	G082291	0.066
21	G082292	0.052
23	G082294	0.114
35	G082306	0.065
42	G082313	0.067
49	G082320	0.066
56	G082327	0.066
57	G082328	0.219
62	G082333	0.077
78	G082349	0.062
79	G082350	0.067
87	G082358	0.066

QC DATA:


Repeat:

9 G082280 0.064

Standard:

MP2 0.279
MP2 0.284

JJ/jl
XLS/07

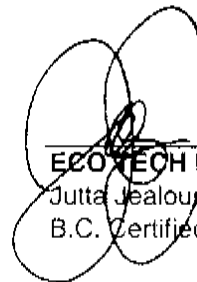

ECOTECH LABORATORY LTD.
Jutta Jealous
B.C. Certified Assayer

ECO TECH LABORATORY LTD.

10041 Dallas Drive
KAMLOOPS, B.C.
V2C 6T4

ICP CERTIFICATE OF ANALYSIS AK 2007- 1317

Pacific Cascade Resources

520 - 700 W. Pender Street
Vancouver, BC
V6C 1G8

Phone: 250-573-5700

Fax : 250-573-4557

No. of samples received: 90

Sample Type: Core

Project: Crack Moly

Shipment #: 3

Submitted by: Pacific Cascade Resources

Values in ppm unless otherwise reported

Et #.	Tag #	Ag	Al%	As	Ba	Bi	Ca%	Cd	Co	Cr	Cu	Fe%	K%	La	Mg%	Mn	Mo	Na%	Ni	P	Pb	Sb	Sn	Sr	Ti%	U	V	W	Y	Zn
1	G082272	<0.2	5.56	5	505	<5	1.79	<1	1	77	18	1.28	0.75	<10	0.31	253	79	2.17	4	400	22	<5	<20	508	0.16	<10	20	<10	2	42
2	G082273	0.4	6.60	<5	615	<5	2.34	2	2	108	17	1.58	0.95	<10	0.40	289	43	2.52	6	480	24	<5	<20	612	0.20	<10	24	<10	2	110
3	G082274	0.4	6.57	10	525	<5	1.78	15	2	137	128	1.68	1.25	<10	0.31	288	50	2.18	7	490	24	<5	<20	492	0.17	<10	29	<10	2	486
4	G082275	0.3	7.19	5	550	<5	2.55	<1	2	108	13	1.51	0.68	<10	0.38	288	17	2.58	5	490	24	<5	<20	658	0.19	<10	25	<10	2	65
5	G082276	0.3	6.81	5	570	<5	2.31	<1	2	106	29	1.55	0.88	<10	0.38	303	29	2.41	6	470	24	<5	<20	600	0.19	<10	29	<10	2	124
6	G082277	0.4	7.05	20	585	<5	2.02	<1	2	106	67	1.70	1.29	<10	0.34	317	104	2.10	5	470	28	<5	<20	546	0.18	<10	27	<10	2	79
7	G082278	1.2	7.31	5	625	<5	1.77	2	3	139	680	2.27	1.57	<10	0.36	323	198	1.91	6	490	28	<5	<20	449	0.16	<10	26	<10	2	110
8	G082279	1.3	6.17	5	620	<5	2.09	<1	2	111	363	1.78	0.97	<10	0.37	303	226	2.28	6	450	22	<5	<20	596	0.18	<10	26	<10	2	72
9	G082280	0.4	7.57	10	910	<5	1.83	<1	6	21	123	2.92	2.63	30	0.60	687	658	1.78	18	940	36	<5	<20	329	0.27	<10	44	<10	16	94
10	G082281	0.6	9.09	10	1145	<5	2.56	<1	3	47	117	2.24	2.52	<10	0.46	511	157	2.69	4	660	36	<5	<20	572	0.22	<10	22	<10	3	72
11	G082282	0.6	6.96	20	610	<5	2.02	2	2	115	132	1.76	1.15	<10	0.37	290	68	2.31	6	480	24	<5	<20	525	0.18	<10	27	<10	2	78
12	G082283	0.8	6.70	80	585	<5	2.01	2	2	134	209	1.81	1.17	<10	0.37	323	117	2.11	6	470	24	<5	<20	511	0.18	<10	27	<10	2	109
13	G082284	0.5	6.49	125	535	<5	1.98	6	2	145	62	1.54	0.98	<10	0.34	286	117	2.15	6	450	26	<5	<20	517	0.17	<10	22	<10	2	182
14	G082285	0.2	7.95	10	890	<5	1.79	<1	2	119	91	2.13	1.78	<10	0.43	387	109	1.90	7	430	30	<5	<20	514	0.20	<10	30	<10	2	86
15	G082286	2.4	7.51	10	925	<5	1.24	4	3	103	1334	2.45	2.11	<10	0.42	387	299	1.80	6	430	28	<5	<20	438	0.20	<10	31	10	2	176
16	G082287	0.6	6.00	10	535	<5	1.94	3	2	125	187	1.62	0.90	<10	0.33	307	106	2.27	5	420	26	<5	<20	536	0.17	<10	25	150	2	89
17	G082288	0.4	6.85	5	605	<5	2.24	1	2	107	108	1.70	1.00	<10	0.38	334	107	2.44	5	480	24	<5	<20	590	0.19	<10	26	<10	2	89
18	G082289	0.4	6.46	5	570	<5	2.29	<1	2	107	19	1.48	0.75	<10	0.37	308	115	2.37	6	430	26	<5	<20	620	0.18	<10	26	<10	2	55
19	G082290	0.2	5.68	5	465	<5	1.74	<1	1	83	46	1.30	0.70	<10	0.32	244	139	2.37	5	390	20	<5	<20	517	0.16	<10	22	<10	2	57
20	G082291	0.3	7.00	10	905	<5	1.69	<1	6	21	130	2.80	2.90	30	0.59	640	657	1.75	17	860	30	<5	<20	328	0.26	<10	42	<10	15	94
21	G082292	<0.2	6.82	30	4005	<5	1.84	<1	1	127	57	1.62	1.32	<10	0.28	296	524	1.91	6	430	24	<5	<20	489	0.17	<10	25	<10	2	54
22	G082293	0.5	6.37	5	495	5	2.32	<1	2	111	40	1.56	0.80	<10	0.32	265	72	2.31	5	460	22	<5	<20	549	0.19	<10	26	<10	2	48
23	G082294	0.6	6.16	5	550	<5	2.09	<1	1	116	25	1.53	0.88	<10	0.36	305	1121	2.42	5	340	22	<5	<20	546	0.18	<10	25	10	1	49
24	G082295	0.6	6.18	<5	550	<5	1.89	<1	2	116	149	1.70	0.99	<10	0.35	331	170	2.05	5	390	20	<5	<20	511	0.18	<10	24	<10	2	93
25	G082296	0.9	7.21	5	780	<5	1.92	<1	2	110	322	1.77	1.72	<10	0.34	352	161	2.43	5	470	28	<5	<20	521	0.18	<10	25	<10	6	74

Et #	Tag #	Ag	Al%	As	Ba	Bi	Ca%	Cd	Co	Cr	Cu	Fe%	K%	La	Mg%	Mn	Mo	Na%	Ni	P	Pb	Sb	Sn	Sr	Ti%	U	V	W	Y	Zn
26	G082297	1.9	6.35	35	1260	10	0.88	6	2	118	883	2.00	2.44	<10	0.19	264	168	0.74	4	300	26	<5	<20	193	0.09	<10	12	20	8	229
27	G082298	1.0	7.04	5	740	<5	2.02	3	2	115	375	1.90	1.28	<10	0.37	378	186	2.24	7	470	26	<5	<20	557	0.19	<10	26	<10	2	148
28	G082299	1.2	6.66	5	600	<5	2.05	<1	2	134	199	1.63	0.84	<10	0.36	408	144	2.18	5	450	26	<5	<20	563	0.17	<10	22	<10	2	59
29	G082300	0.6	6.77	10	685	<5	2.34	<1	2	112	169	1.98	1.27	<10	0.39	401	63	2.39	6	470	26	<5	<20	505	0.21	<10	32	<10	1	76
30	G082301	0.7	6.85	5	505	<5	2.39	<1	2	103	19	1.75	1.00	<10	0.36	348	430	2.52	5	490	24	<5	<20	555	0.20	<10	28	<10	2	58
31	G082302	0.2	5.02	<5	445	<5	1.31	<1	2	134	85	1.54	1.05	<10	0.28	258	259	1.58	6	330	20	<5	<20	373	0.14	<10	20	<10	1	41
32	G082303	1.0	6.13	10	535	<5	1.77	<1	2	113	451	1.76	1.08	<10	0.34	312	165	2.08	5	480	22	<5	<20	469	0.17	<10	29	<10	1	79
33	G082304	0.8	6.65	5	1000	<5	1.89	2	2	103	106	1.53	1.45	<10	0.30	326	103	2.15	6	350	24	<5	<20	548	0.14	<10	20	60	5	102
34	G082305	0.3	6.71	40	840	<5	1.47	<1	1	102	77	1.41	1.51	<10	0.23	262	52	2.17	5	320	28	<5	<20	398	0.12	<10	15	<10	8	80
35	G082306	0.5	7.05	10	925	<5	1.65	<1	6	21	131	2.84	2.31	30	0.60	633	666	1.57	17	890	32	<5	<20	332	0.27	<10	46	<10	16	96
36	G082307	0.6	6.87	10	1070	5	1.53	6	1	104	224	1.68	1.73	10	0.28	363	93	2.05	5	370	26	<5	<20	451	0.14	<10	20	<10	7	259
37	G082308	<0.2	6.52	5	615	<5	1.84	<1	1	118	57	1.82	1.31	<10	0.31	359	323	2.00	6	430	22	<5	<20	477	0.18	<10	27	<10	2	102
38	G082309	0.3	7.06	5	615	<5	2.11	<1	1	72	90	1.82	1.13	<10	0.38	436	147	2.15	6	500	22	<5	<20	571	0.19	<10	31	<10	2	80
39	G082310	<0.2	6.57	5	610	<5	1.94	<1	1	58	87	1.79	1.13	<10	0.38	383	211	2.07	5	480	22	<5	<20	510	0.19	<10	29	<10	2	80
40	G082311	0.3	5.78	<5	520	<5	1.93	<1	1	130	70	1.58	0.95	<10	0.34	354	152	2.14	6	410	22	<5	<20	493	0.18	<10	27	<10	2	100
41	G082312	<0.2	5.86	<5	500	<5	1.90	<1	1	131	38	1.60	0.87	<10	0.34	365	199	2.11	6	450	22	<5	<20	502	0.19	<10	28	<10	2	94
42	G082313	0.3	6.71	5	865	<5	1.70	<1	6	21	134	2.63	3.13	30	0.58	579	632	1.53	17	850	32	<5	<20	317	0.24	<10	47	<10	16	92
43	G082314	<0.2	8.70	10	900	<5	2.38	<1	1	75	92	1.87	2.53	<10	0.40	399	110	2.73	4	560	34	<5	<20	551	0.19	<10	20	<10	3	55
44	G082315	0.2	6.54	<5	575	<5	2.39	2	2	115	58	1.68	0.97	<10	0.38	324	54	2.50	7	530	22	<5	<20	567	0.20	<10	30	<10	2	122
45	G082316	0.4	8.68	10	765	<5	2.00	4	3	130	246	3.06	2.24	10	0.45	400	113	2.13	7	620	28	<5	<20	516	0.23	<10	32	20	2	197
46	G082317	<0.2	8.27	10	685	<5	2.01	<1	2	109	140	2.77	1.93	<10	0.44	418	305	2.15	6	410	26	<5	<20	515	0.24	<10	35	10	2	119
47	G082318	0.4	6.22	<5	630	<5	1.57	3	1	121	109	1.86	1.36	<10	0.31	339	162	1.98	6	350	24	<5	<20	430	0.18	<10	26	<10	3	235
48	G082319	0.6	6.51	40	1270	10	0.33	5	<1	114	339	1.82	2.98	<10	0.13	128	124	0.59	4	230	24	<5	<20	127	0.05	<10	7	10	7	344
49	G082320	<0.2	6.15	<5	490	<5	1.92	1	1	134	77	1.84	1.08	<10	0.33	312	658	2.02	6	470	22	<5	<20	451	0.17	<10	28	<10	2	108
50	G082321	0.8	6.64	5	550	<5	2.47	<1	1	68	25	1.68	0.93	<10	0.39	365	62	2.68	6	540	26	<5	<20	595	0.21	<10	30	<10	2	65
51	G082322	0.8	5.91	5	495	<5	2.24	1	2	104	71	1.51	0.80	<10	0.35	327	306	2.31	6	480	22	<5	<20	547	0.18	<10	29	<10	1	113
52	G082323	0.6	6.55	5	605	<5	2.24	<1	2	109	53	1.65	0.97	<10	0.38	366	145	2.70	6	530	26	<5	<20	591	0.20	<10	31	<10	2	72
53	G082324	0.2	6.54	5	600	<5	2.38	<1	2	119	68	1.55	0.84	<10	0.39	340	17	2.76	7	500	24	<5	<20	614	0.20	<10	29	<10	1	62
54	G082325	0.2	6.33	5	525	<5	2.41	<1	2	125	59	1.50	0.83	<10	0.35	347	39	2.25	7	470	24	<5	<20	535	0.18	<10	27	<10	2	66
55	G082326	0.2	6.82	<5	655	<5	1.90	<1	2	122	179	2.08	1.54	<10	0.34	336	95	2.02	6	510	24	<5	<20	494	0.19	<10	27	<10	3	72
56	G082327	0.4	6.90	10	855	<5	1.71	<1	5	21	130	2.62	2.98	30	0.56	571	668	1.56	17	820	32	<5	<20	317	0.24	<10	45	<10	15	86
57	G082328	0.5	5.10	35	460	5	1.07	<1	<1	148	231	1.77	1.34	<10	0.25	234	2113	1.37	5	400	16	<5	<20	309	0.12	<10	19	<10	2	57
58	G082329	0.4	6.30	5	1555	<5	0.82	<1	<1	100	245	0.97	3.08	20	0.06	103	222	1.63	4	170	26	<5	<20	314	0.03	<10	2	<10	13	30
59	G082330	<0.2	6.36	5	645	<5	1.68	<1	1	132	98	1.94	1.72	<10	0.32	413	123	1.59	6	470	22	<5	<20	418	0.16	<10	24	<10	2	95
60	G082331	1.2	5.31	90	580	5	0.28	3	2	179	530	2.59	2.08	<10	0.24	280	120	0.59	7	460	20	5	<20	104	0.13	<10	22	<10	2	186
61	G082332	1.0	6.38	15	625	45	1.44	1	2	108	393	2.27	1.55	<10	0.34	461	46	1.67	7	550	28	<5	<20	389	0.16	<10	25	<10	2	125
62	G082333	0.6	6.04	5	620	<5	1.03	<1	3	142	297	2.38	1.80	<10	0.31	355	735	1.41	6	500	22	<5	<20	360	0.16	<10	22	<10	2	94
63	G082334	1.4	7.47	5	690	<5	2.08	1	2	118	544	2.24	1.38	<10	0.38	452	23	2.11	6	550	24	<5	<20	548	0.19	<10	27	<10	2	117
64	G082335	1.8	6.78	5	665	<5	1.83	<1	2	140	834	2.11	1.29	<10	0.36	431	32	2.18	7	520	24	<5	<20	537	0.18	<10	27	<10	2	105
65	G082336	1.2	6.58	20	695	35	1.44	2	1	106	608	2.17	1.56	<10	0.39	380	324	1.61	6	480	24	<5	<20	402	0.16	<10	25	<10	2	140

Et #.	Tag #	Ag	Al%	As	Ba	Bi	Ca%	Cd	Co	Cr	Cu	Fe%	K%	La	Mg%	Mn	Mo	Na%	Ni	P	Pb	Sb	Sn	Sr	Ti%	U	V	W	Y	Zn
66	G082337	0.4	6.81	10	600	<5	1.71	<1	1	103	126	1.73	1.37	10	0.25	293	63	2.12	5	390	24	<5	<20	477	0.13	<10	19	<10	8	67
67	G082338	1.0	6.76	30	600	5	1.89	3	1	98	234	1.77	1.19	<10	0.36	363	39	2.27	5	510	24	<5	<20	542	0.18	<10	28	<10	3	256
68	G082339	2.4	6.53	30	590	<5	1.76	1	2	164	816	2.14	1.43	<10	0.29	391	108	1.73	8	510	22	<5	<20	418	0.17	<10	23	<10	2	126
69	G082340	0.5	6.96	100	655	<5	2.06	1	1	129	249	2.18	1.67	<10	0.33	421	176	1.79	7	560	24	<5	<20	425	0.18	<10	27	<10	3	69
70	G082341	3.0	7.11	10	970	<5	1.64	<1	2	87	1298	2.59	1.81	<10	0.35	472	20	1.71	6	490	24	<5	<20	405	0.17	<10	25	<10	5	111
71	G082342	3.4	7.34	5	975	<5	1.47	4	2	82	1719	2.57	1.75	<10	0.36	463	9	1.51	5	490	26	<5	<20	435	0.17	<10	24	<10	5	209
72	G082343	1.6	7.09	5	755	10	1.69	2	2	106	716	2.29	1.57	<10	0.35	484	22	1.97	5	460	24	<5	<20	484	0.17	<10	25	10	4	159
73	G082344	2.1	6.93	5	740	<5	1.59	2	2	115	1080	2.18	1.66	<10	0.30	379	107	1.73	6	430	26	<5	<20	453	0.15	<10	21	<10	7	137
74	G082345	1.9	6.82	5	620	<5	1.87	1	2	118	809	2.40	1.39	<10	0.34	483	204	2.05	6	440	24	<5	<20	478	0.18	<10	24	<10	3	137
75	G082346	4.4	5.80	<5	660	<5	0.94	2	3	145	1304	2.38	1.68	<10	0.29	528	75	1.04	6	460	22	<5	<20	266	0.15	<10	21	<10	3	194
76	G082347	0.4	7.11	10	660	<5	1.84	<1	2	99	99	2.34	1.41	<10	0.37	482	42	2.06	6	460	24	<5	<20	514	0.18	<10	25	<10	3	99
77	G082348	0.4	7.52	5	730	<5	1.70	<1	3	111	184	2.76	1.74	<10	0.37	635	174	1.82	7	490	24	<5	<20	486	0.18	<10	27	<10	4	113
78	G082349	0.7	7.15	5	685	<5	1.77	2	2	111	269	2.48	1.44	<10	0.37	593	639	2.00	6	500	26	<5	<20	501	0.20	<10	26	<10	3	235
79	G082350	0.4	7.24	5	905	<5	1.64	<1	6	20	128	2.78	2.57	30	0.59	630	666	1.64	16	870	32	<5	<20	333	0.26	<10	44	<10	15	93
80	G082351	0.4	9.13	10	1070	<5	2.59	<1	3	46	132	2.23	2.36	<10	0.47	514	146	2.62	5	610	38	<5	<20	555	0.22	<10	23	<10	3	74
81	G082352	6.8	6.03	10	1380	10	0.48	4	<1	107	1715	1.84	3.11	10	0.04	285	32	1.02	3	160	32	<5	<20	172	0.03	<10	2	<10	15	212
82	G082353	1.1	6.45	15	620	<5	1.72	2	3	111	706	1.94	1.14	<10	0.37	390	103	2.10	6	490	24	<5	<20	508	0.19	<10	28	<10	2	148
83	G082354	0.2	7.34	10	615	<5	2.42	<1	2	109	88	1.83	0.95	<10	0.42	399	65	2.65	6	540	26	<5	<20	646	0.23	<10	31	<10	3	99
84	G082355	0.6	6.83	115	605	<5	2.13	1	2	114	163	1.97	0.99	<10	0.38	384	65	2.53	7	530	28	<5	<20	597	0.20	<10	28	<10	3	108
85	G082356	0.2	6.64	10	560	<5	2.39	<1	2	101	124	1.65	0.76	<10	0.39	423	50	2.69	5	520	26	<5	<20	600	0.21	<10	29	<10	2	122
86	G082357	0.2	6.65	5	660	<5	2.27	4	2	102	177	1.65	1.01	<10	0.32	373	12	2.38	5	460	24	<5	<20	599	0.18	<10	26	30	5	209
87	G082358	0.4	7.68	10	920	<5	1.76	<1	6	20	126	2.92	2.25	30	0.60	647	661	1.64	18	920	36	<5	<20	338	0.27	<10	45	<10	15	99
88	G082359	<0.2	6.79	10	1030	<5	1.79	7	2	99	141	1.51	1.56	<10	0.32	384	29	2.33	5	390	26	<5	<20	565	0.16	<10	22	<10	7	295
89	G082360	0.5	6.51	15	485	5	2.18	4	2	116	246	1.67	1.37	<10	0.29	454	20	2.45	7	440	24	<5	<20	423	0.17	<10	30	<10	2	208
90	G082361	0.2	6.70	15	655	<5	2.01	8	1	97	202	1.74	1.40	<10	0.35	393	28	2.44	5	450	24	<5	<20	529	0.19	<10	26	40	3	513

QC DATA:

Repeat:


1	G082272	<0.2	5.51	5	500	<5	1.73	<1	2	74	16	1.28	0.76	<10	0.30	253	76	2.05	4	390	20	<5	<20	483	0.16	<10	20	<10	2	43
10	G082281	0.6	9.33	10	1180	<5	2.69	<1	2	47	117	2.28	2.45	<10	0.47	523	153	2.85	6	700	38	<5	<20	581	0.22	<10	22	<10	4	74
19	G082290	0.2	5.93	5	485	<5	1.77	<1	1	89	44	1.30	0.95	<10	0.35	244	135	2.54	5	450	22	<5	<20	535	0.16	<10	22	<10	2	67
36	G082307	0.5	6.87	5	1015	<5	1.54	6	1	102	224	1.67	1.81	10	0.28	345	98	1.99	6	360	26	<5	<20	443	0.14	<10	20	<10	7	255
45	G082316	0.4	8.67	5	745	<5	2.00	3	3	123	236	2.98	2.11	<10	0.44	396	113	2.04	8	600	28	<5	<20	502	0.23	<10	32	20	2	189
54	G082325	0.6	6.50	10	555	<5	2.38	<1	1	132	61	1.53	0.88	<10	0.37	344	40	2.36	6	480	26	<5	<20	564	0.18	<10	26	<10	2	67
71	G082342	3.2	7.29	5	975	<5	1.49	4	2	80	1740	2.63	1.76	<10	0.36	460	10	1.60	4	490	26	<5	<20	419	0.17	<10	23	<10	5	205
80	G082351	0.3	9.01	10	1110	<5	2.59	<1	2	54	134	2.26	2.34	<10	0.48	514	127	2.79	5	610	34	<5	<20	572	0.22	<10	21	<10	3	74
90	G082361	0.4	6.75	15	670	<5	2.08	5	2	107	200	1.71	1.38	<10	0.39	400	28	2.42	5	460	24	<5	<20	506	0.18	<10	26	<10	2	518

Resplit:


1	G082272	<0.2	5.34	<5	470	<5	1.64	<1	2	71	18	1.33	0.76	<10	0.29	245	74	2.09	5	390	20	<5	<20	479	0.15	<10	21	<10	1	42
36	G082307	0.4	6.72	10	1005	<5	1.48	6	1	108	239	1.74	1.77	<10	0.28	353	99	2.05	4	360	26	<5	<20	437	0.14	<10	19	<10	7	257
71	G082342	3.1	7.36	10	935	5	1.60	4	2	54	1793	2.61	1.74	<10	0.35	454	10	1.50	6	470	28	<5	<20	427	0.17	<10	24	<10	5	211

Et #.	Tag #	Ag	Al%	As	Ba	Bi	Ca%	Cd	Co	Cr	Cu	Fe%	K%	La	Mg%	Mn	Mo	Na%	Ni	P	Pb	Sb	Sn	Sr	Ti%	U	V	W	Y	Zn	
<i>Standard:</i>																															
STSD3		0.9	5.77	30	1395	<5	2.33	1	17	60	38	4.12	1.34	30	1.29	2523	7	0.97	32	1620	52	<5	<20	260	0.35	<10	113	<10	32	205	
STSD3		0.5	5.81	25	1415	<5	2.48	1	17	63	42	4.22	1.39	30	1.30	2568	6	1.05	32	1680	54	<5	<20	254	0.34	<10	116	<10	32	204	
STSD3		0.5	5.86	25	1430	<5	2.49	1	17	62	43	4.20	1.39	40	1.30	2563	7	1.08	32	1680	54	<5	<20	266	0.35	<10	121	<10	32	207	

JJ/nl
 dl:td1317aS:td1317bS
 XLS/07

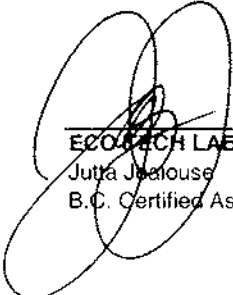

 ECO TECH LABORATORY LTD.
 Jutta Jalouse
 B.C. Certified Assayer

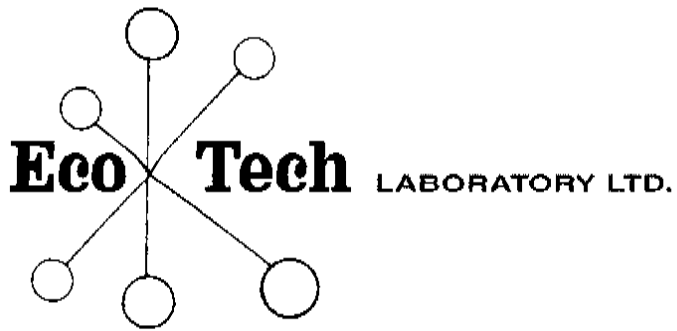

ASSAYING, GEOCHEMISTRY
ANALYTICAL CHEMISTRY
ENVIRONMENTAL TESTING
ISO 9001 Accredited Co.

10041 Dallas Drive, Kamloops, BC V2C 6T4
Phone (250) 573-5700 Fax (250) 573-4557
E-mail: info@ecotechlab.com
www.ecotechlab.com

CERTIFICATE OF ASSAY AK 2007-1316

Pacific Cascade Resources
520 - 700 W. Pender Street
Vancouver, BC
V6C 1G8

17-Sep-07

No. of samples received: 146
Sample Type: Core
Project: Crack Moly
Shipment #: 2
Submitted by: Pacific Cascade Resources

ET #.	Tag #	W (%)
58	G082183	0.084
59	G082184	0.688
66	G082191	0.126


QC DATA:

Repeat:


58	G082183	0.083
59	G082184	0.682
66	G082191	0.128

Standard:

MP2 0.641

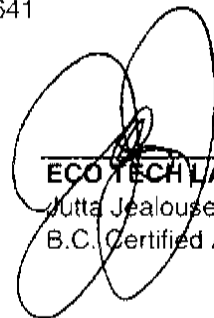
ECO TECH LABORATORY LTD.
Jutta Jealous
B.C. Certified Assayer

JJ/nl
XLS/07

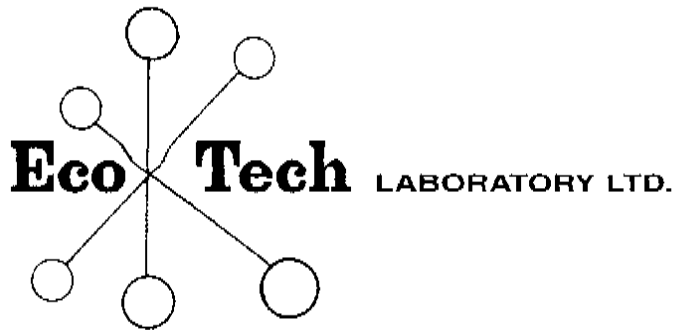

ASSAYING, GEOCHEMISTRY
ANALYTICAL CHEMISTRY
ENVIRONMENTAL TESTING
ISO 9001 Accredited Co.

10041 Dallas Drive, Kamloops, BC V2C 6T4
Phone (250) 573-5700 Fax (250) 573-4557
E-mail: info@ecotechlab.com
www.ecotechlab.com


CERTIFICATE OF ASSAY AK 2007-1316

Pacific Cascade Resources
520 - 700 W. Pender Street
Vancouver, BC
V6C 1G8

14-Sep-07

No. of samples received: 146
Sample Type: Core
Project: Crack Moly
Shipment #: 2
Submitted by: Pacific Cascade Resources

ET #.	Tag #	Mo (%)
5	G082130	0.066
14	G082139	0.066
20	G082145	0.058
25	G082150	0.061
29	G082154	0.067
40	G082165	0.086
46	G082171	0.066
47	G082172	0.050
56	G082181	0.054
58	G082183	0.024
62	G082187	0.068
68	G082193	0.068
79	G082204	0.063
81	G082206	0.069
82	G082207	0.074
89	G082214	0.067
101	G082226	0.067
103	G082228	0.072
108	G082233	0.066
109	G082234	0.328
111	G082236	0.066
114	G082239	0.323
115	G082240	0.655
116	G082241	0.363
122	G082247	0.067
129	G082254	0.072
130	G082255	0.065

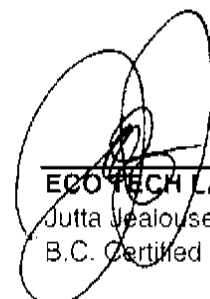

ECO TECH LABORATORY LTD.
Jutta Jealouse
B.C. Certified Assayer

Pacific Cascade Resources AK7 - 1316

<u>ET #.</u>	<u>Tag #</u>	<u>Mo (%)</u>
132	G082257	0.066
136	G082261	0.080
140	G082265	0.067
142	G082267	1.426

QC DATA:

Repeat:

25	G082150	0.064
115	G082240	0.647
129	G082254	0.071
142	G082267	1.425

Standard:

MP2	0.282
MP2	0.280

JJ/jl
XLS/07



ECO TECH LABORATORY LTD.

Jutta Jealous

B.C. Certified Assayer

ECO TECH LABORATORY LTD.

10041 Dallas Drive

KAMLOOPS, B.C.

V2C 6T4

ICP CERTIFICATE OF ANALYSIS AK 2007- 1316

Pacific Cascade Resources

520 - 700 W. Pender Street

Vancouver, BC

V6C 1G8

Phone: 250-573-5700

Fax : 250-573-4557

No. of samples received: 146

Sample Type: Core

Project: Crack Moly

Shipment #: 2

Submitted by: Pacific Cascade Resources

Values in ppm unless otherwise reported


Et #.	Tag #	Ag	Al%	As	Ba	Bi	Ca%	Cd	Co	Cr	Cu	Fe%	K%	La	Mg%	Mn	Mo	Na%	Ni	P	Pb	Sb	Sn	Sr	Ti%	U	V	W	Y	Zn
1	G082126	0.4	5.82	110	1550	<5	0.64	1	<1	43	17	0.51	3.02	10	0.06	109	441	1.30	3	270	46	<5	<20	243	0.04	<10	4	<10	9	101
2	G082127	0.2	5.39	15	1865	<5	0.59	1	<1	86	18	0.54	3.44	10	0.07	96	38	1.01	3	180	44	<5	<20	261	0.03	<10	4	<10	10	227
3	G082128	0.3	6.70	5	515	<5	2.26	<1	<1	98	40	1.79	1.27	<10	0.33	397	408	1.94	6	530	30	<5	<20	473	0.18	<10	22	10	3	94
4	G082129	0.2	5.09	35	1115	<5	1.03	<1	<1	92	22	0.65	2.52	10	0.08	111	112	1.19	4	190	34	<5	<20	206	0.03	<10	3	<10	9	39
5	G082130	0.6	7.28	10	1000	<5	2.12	<1	6	22	129	2.83	2.98	30	0.65	783	651	1.36	21	1060	46	<5	<20	373	0.31	<10	44	<10	16	120
6	G082131	0.2	5.28	20	1170	<5	0.79	<1	<1	82	27	0.66	2.73	10	0.08	124	61	1.37	3	190	38	<5	<20	204	0.03	<10	4	40	10	50
7	G082132	0.3	6.11	370	935	<5	1.18	2	<1	80	24	0.70	2.47	20	0.08	128	17	1.58	5	230	38	<5	<20	205	0.04	<10	2	<10	12	28
8	G082133	<0.2	6.23	10	470	<5	1.96	<1	1	92	34	1.91	1.24	<10	0.29	433	283	1.97	6	480	26	<5	<20	423	0.16	<10	20	30	4	58
9	G082134	0.2	6.63	5	600	<5	2.04	<1	2	89	59	1.93	1.28	<10	0.29	431	203	2.00	6	570	28	<5	<20	451	0.16	<10	19	<10	6	62
10	G082135	<0.2	6.82	<5	620	<5	2.17	<1	2	49	7	1.96	1.43	<10	0.34	384	147	2.13	4	610	24	<5	<20	492	0.19	<10	22	<10	4	65
11	G082136	<0.2	6.72	5	1630	<5	1.07	<1	<1	86	24	0.60	3.28	20	0.06	121	195	1.69	4	200	36	<5	<20	309	0.04	<10	3	<10	16	53
12	G082137	0.2	6.01	15	500	<5	1.72	<1	1	105	41	1.80	1.36	<10	0.25	354	275	2.05	5	330	22	<5	<20	350	0.14	<10	18	<10	5	58
13	G082138	0.2	6.52	35	1605	<5	0.92	1	<1	82	22	0.62	3.02	10	0.08	118	93	1.71	3	210	40	<5	<20	287	0.03	<10	3	40	12	89
14	G082139	0.4	7.32	5	945	<5	1.87	<1	5	21	132	2.91	3.02	30	0.62	696	643	1.50	19	960	40	<5	<20	326	0.29	<10	44	<10	16	103
15	G082140	0.3	6.93	5	545	<5	2.32	<1	2	100	39	1.95	1.31	<10	0.33	359	27	2.40	5	490	28	<5	<20	483	0.17	<10	22	<10	4	72
16	G082141	0.4	6.48	15	1415	<5	0.73	<1	<1	72	9	0.71	2.96	10	0.05	135	161	1.89	3	160	42	<5	<20	180	0.03	<10	2	<10	10	34
17	G082142	0.4	6.10	75	1325	<5	0.83	<1	<1	69	19	0.67	3.31	10	0.07	113	17	1.81	3	220	40	<5	<20	206	0.04	<10	2	<10	12	37
18	G082143	0.2	6.41	105	515	<5	2.11	2	2	97	73	2.08	1.69	<10	0.32	380	120	1.81	6	580	30	<5	<20	358	0.15	<10	21	<10	4	123
19	G082144	0.2	6.85	40	585	<5	2.31	<1	1	99	36	2.25	1.51	<10	0.40	442	140	2.19	6	630	32	<5	<20	460	0.20	<10	24	<10	3	76
20	G082145	0.2	6.79	15	655	<5	1.64	<1	1	105	30	2.23	1.84	<10	0.33	394	583	2.02	7	450	30	<5	<20	399	0.17	<10	22	<10	4	64
21	G082146	<0.2	6.35	10	1420	<5	0.83	<1	<1	71	16	0.71	3.53	20	0.07	126	28	1.99	3	250	40	<5	<20	188	0.04	<10	2	<10	12	40
22	G082147	0.3	5.66	10	1320	<5	0.71	<1	<1	75	19	0.63	3.36	20	0.05	103	48	1.71	3	220	38	<5	<20	173	0.04	<10	2	<10	11	28
23	G082148	0.2	6.15	15	1235	<5	0.71	<1	<1	67	51	0.77	3.28	20	0.06	117	95	1.66	3	240	38	<5	<20	162	0.04	<10	3	<10	11	54
24	G082149	0.4	5.84	<5	1380	<5	0.68	<1	<1	63	10	0.56	3.44	10	0.04	98	14	1.92	3	220	40	<5	<20	172	0.03	<10	2	<10	11	28
25	G082150	<0.2	6.99	<5	630	<5	2.39	<1	<1	71	44	2.26	1.66	<10	0.32	493	620	2.63	5	720	30	<5	<20	473	0.20	<10	23	<10	5	63

Et #.	Tag #	Ag	Al%	As	Ba	Bi	Ca%	Cd	Co	Cr	Cu	Fe%	K%	La	Mg%	Mn	Mo	Na%	Ni	P	Pb	Sb	Sn	Sr	Ti%	U	V	W	Y	Zn
26	G082151	0.4	6.10	10	505	<5	1.37	1	2	99	74	2.05	1.38	<10	0.35	438	77	2.13	6	620	28	<5	<20	441	0.17	<10	24	<10	4	103
27	G082152	0.2	5.80	<5	590	<5	2.55	<1	2	95	12	1.58	0.90	<10	0.41	320	25	2.42	6	500	26	<5	<20	561	0.21	<10	28	<10	2	55
28	G082153	0.4	6.45	<5	565	<5	1.90	<1	2	110	33	2.16	1.46	<10	0.32	450	75	2.05	6	520	26	<5	<20	439	0.17	<10	22	<10	3	67
29	G082154	0.6	6.66	5	890	<5	1.69	<1	5	19	126	2.71	2.42	30	0.58	637	648	1.52	18	850	34	<5	<20	290	0.27	<10	41	<10	14	94
30	G082155	0.2	6.24	25	495	<5	1.83	<1	1	97	45	2.12	1.46	<10	0.34	486	184	2.01	6	500	26	<5	<20	421	0.18	<10	23	<10	3	136
31	G082156	<0.2	6.08	5	465	<5	1.92	<1	2	114	41	2.21	1.35	<10	0.31	476	235	2.05	6	540	24	<5	<20	410	0.18	<10	23	<10	2	65
32	G082157	0.6	6.74	<5	525	<5	2.02	<1	1	107	46	2.18	1.38	<10	0.30	440	292	2.18	6	480	28	<5	<20	442	0.17	<10	20	<10	3	96
33	G082158	0.2	6.22	10	1520	<5	0.69	<1	<1	70	28	0.57	3.48	10	0.03	87	18	1.87	3	150	44	<5	<20	201	0.03	<10	2	<10	9	31
34	G082159	0.4	6.15	15	1445	<5	0.67	<1	<1	75	49	0.64	3.43	10	0.05	95	306	1.62	2	160	36	<5	<20	207	0.03	<10	3	<10	9	47
35	G082160	0.3	5.92	<5	1375	<5	0.68	<1	<1	78	28	0.54	3.24	10	0.06	99	97	1.50	3	140	40	<5	<20	206	0.02	<10	3	<10	7	18
36	G082161	0.6	6.24	15	1390	<5	0.71	<1	<1	69	49	0.63	3.34	10	0.05	77	94	2.04	3	150	38	<5	<20	207	0.03	<10	2	<10	8	37
37	G082162	0.4	6.69	290	690	<5	1.99	1	1	56	29	1.63	1.42	<10	0.31	319	38	2.36	6	460	28	<5	<20	496	0.18	<10	23	<10	4	53
38	G082163	0.6	6.20	90	495	<5	2.57	<1	1	95	6	1.41	1.27	<10	0.25	282	189	2.08	6	410	24	<5	<20	492	0.15	<10	20	<10	4	43
39	G082164	0.5	6.57	5	515	<5	2.55	<1	2	97	12	1.71	0.98	<10	0.32	307	87	2.47	6	510	28	<5	<20	529	0.21	<10	26	<10	2	54
40	G082165	0.3	7.26	20	670	<5	2.63	<1	<1	125	10	2.03	1.73	<10	0.37	380	894	2.09	8	620	28	<5	<20	510	0.22	<10	29	<10	3	67
41	G082166	0.2	6.35	<5	430	<5	2.38	<1	2	94	25	1.97	1.10	<10	0.33	334	201	2.57	6	510	28	<5	<20	474	0.19	<10	25	<10	3	62
42	G082167	0.3	6.19	<5	1635	<5	0.71	<1	<1	75	39	0.60	3.11	10	0.04	83	80	2.07	3	150	36	<5	<20	206	0.03	<10	2	<10	10	37
43	G082168	0.2	5.96	<5	1445	<5	0.67	<1	<1	72	42	0.63	2.82	10	0.04	100	231	1.97	3	190	36	<5	<20	194	0.03	<10	2	<10	10	51
44	G082169	0.5	6.91	5	555	<5	1.83	<1	2	120	110	2.24	1.31	<10	0.31	411	143	2.18	7	510	30	<5	<20	452	0.18	<10	22	<10	4	65
45	G082170	0.8	6.94	<5	740	<5	1.88	<1	1	103	37	1.97	1.43	<10	0.27	385	70	2.23	5	400	34	<5	<20	477	0.15	<10	19	<10	4	66
46	G082171	0.6	7.15	10	955	<5	1.64	<1	5	20	135	2.84	2.28	30	0.58	680	673	1.59	19	930	38	<5	<20	318	0.28	<10	44	<10	15	97
47	G082172	0.4	7.69	10	610	<5	1.97	<1	2	111	116	2.80	1.47	<10	0.39	431	501	2.30	8	570	34	<5	<20	472	0.20	<10	24	<10	3	73
48	G082173	0.6	6.62	35	545	<5	1.97	<1	1	101	80	1.89	1.25	<10	0.28	326	38	2.38	5	420	30	<5	<20	441	0.15	<10	21	<10	4	62
49	G082174	<0.2	6.01	<5	525	<5	1.62	<1	<1	94	25	1.52	0.93	<10	0.31	265	288	2.43	5	450	28	<5	<20	544	0.18	<10	27	<10	3	42
50	G082175	0.6	6.11	5	555	<5	2.27	<1	1	107	41	1.64	1.07	<10	0.31	328	72	2.47	5	420	30	<5	<20	482	0.16	<10	20	<10	3	82
51	G082176	0.5	6.44	<5	525	<5	2.32	<1	2	98	34	1.84	0.99	<10	0.40	358	107	2.43	7	470	30	<5	<20	526	0.19	<10	23	<10	3	57
52	G082177	<0.2	6.40	5	540	<5	2.07	<1	<1	98	61	1.66	1.32	<10	0.29	296	316	2.37	5	520	30	<5	<20	475	0.15	<10	20	<10	3	47
53	G082178	0.5	6.57	5	1785	<5	0.84	<1	<1	69	23	0.56	3.56	10	0.07	88	53	1.63	3	160	42	<5	<20	320	0.03	<10	6	<10	9	21
54	G082179	0.4	6.58	5	1060	<5	1.55	<1	<1	72	23	1.17	2.20	<10	0.23	219	36	2.12	4	330	32	<5	<20	426	0.12	<10	16	<10	6	47
55	G082180	0.4	6.41	<5	615	<5	2.02	<1	1	92	39	1.53	1.34	<10	0.25	291	137	2.61	5	400	30	<5	<20	448	0.14	<10	19	20	5	44
56	G082181	0.6	6.11	5	515	<5	1.87	<1	<1	120	31	1.66	1.15	<10	0.30	327	550	2.14	6	550	28	<5	<20	440	0.15	<10	18	20	5	71
57	G082182	0.5	8.94	10	1180	<5	2.59	<1	2	54	191	2.09	2.45	<10	0.44	429	192	2.76	5	620	42	<5	<20	555	0.22	<10	23	<10	3	58
58	G082183	0.6	6.21	10	580	<5	1.80	<1	1	106	66	1.68	1.25	<10	0.27	310	731	2.16	4	420	30	<5	<20	419	0.13	<10	19	260	6	55
59	G082184	0.4	6.70	15	590	90	2.08	3	9	118	76	1.92	1.47	<10	0.35	362	165	2.33	<1	620	44	<5	<20	457	0.16	<10	25	1790	4	138
60	G082185	0.6	7.10	5	720	<5	2.28	<1	2	90	45	2.13	1.49	<10	0.40	436	171	2.42	5	550	38	<5	<20	557	0.20	<10	25	<10	2	114
61	G082186	0.6	6.27	5	560	<5	2.18	<1	2	104	72	1.99	1.10	<10	0.36	390	144	2.22	8	600	32	<5	<20	522	0.18	<10	24	<10	2	69
62	G082187	0.4	7.07	10	1030	<5	1.82	<1	5	20	149	2.78	2.77	30	0.62	672	674	1.61	17	890	38	<5	<20	333	0.27	<10	43	<10	15	96
63	G082188	0.4	7.46	10	730	<5	2.12	<1	1	90	39	2.02	1.60	<10	0.37	334	153	2.21	6	600	34	<5	<20	532	0.18	<10	23	10	3	51
64	G082189	0.4	7.40	5	805	<5	2.16	<1	1	89	36	1.62	1.67	<10	0.33	293	36	2.55	6	490	34	<5	<20	541	0.16	<10	22	<10	5	44
65	G082190	0.6	6.87	5	1020	<5	1.34	<1	<1	94	32	1.75	1.49	<10	0.31	315	419	2.39	5	470	34	<5	<20	517	0.15	<10	23	<10	4	49

Et #.	Tag #	Ag	Al%	As	Ba	Bi	Ca%	Cd	Co	Cr	Cu	Fe%	K%	La	Mg%	Mn	Mo	Na%	Ni	P	Pb	Sb	Sn	Sr	Ti%	U	V	W	Y	Zn
66	G0821 91	0.6	7.17	20	605	<5	1.27	<1	4	86	126	2.40	1.49	<10	0.38	363	182	2.15	3	630	28	<5	<20	451	0.18	<10	29	380	3	53
67	G0821 92	0.4	6.99	<5	595	<5	1.49	<1	1	92	19	1.84	1.30	<10	0.34	352	149	2.55	4	520	28	<5	<20	536	0.17	<10	25	<10	4	52
68	G0821 93	0.5	7.35	5	1035	<5	1.25	<1	6	20	141	2.87	2.60	30	0.62	660	672	1.65	18	910	36	<5	<20	348	0.27	<10	47	<10	16	97
69	G0821 94	0.2	6.99	5	615	<5	2.13	<1	1	108	51	1.95	1.39	<10	0.37	360	240	2.36	6	610	32	<5	<20	507	0.18	<10	27	<10	3	46
70	G0821 95	0.4	6.97	<5	965	<5	1.95	<1	1	89	29	1.40	1.50	<10	0.29	274	64	2.37	4	400	30	<5	<20	527	0.15	<10	19	<10	6	53
71	G0821 96	0.4	6.22	5	460	<5	2.20	<1	2	62	26	1.51	0.97	<10	0.32	288	47	2.61	4	450	28	<5	<20	496	0.18	<10	25	<10	3	43
72	G0821 97	5.0	6.56	5	510	<5	2.28	<1	1	63	21	1.64	1.08	<10	0.34	334	57	2.62	5	470	30	<5	<20	489	0.19	<10	26	<10	3	47
73	G0821 98	0.5	6.75	10	570	<5	2.14	<1	<1	89	53	1.81	1.18	<10	0.35	346	389	2.52	5	500	30	<5	<20	522	0.18	<10	25	<10	3	50
74	G0821 99	0.6	6.41	5	520	<5	2.28	<1	2	84	24	1.57	1.11	<10	0.30	296	150	2.86	3	470	28	<5	<20	499	0.17	<10	23	110	3	39
75	G0822 00	0.3	6.65	20	550	<5	2.32	<1	1	98	22	1.77	1.11	<10	0.36	347	92	2.66	5	460	26	<5	<20	517	0.18	<10	23	<10	3	51
76	G0822 01	0.4	7.12	5	835	<5	1.68	<1	<1	99	17	1.46	1.67	<10	0.27	286	169	2.51	6	310	34	<5	<20	461	0.14	<10	16	<10	5	53
77	G0822 02	0.4	6.41	10	1700	<5	0.74	<1	<1	51	26	0.46	1.96	<10	0.08	76	42	1.85	2	150	32	<5	<20	324	0.03	<10	5	<10	11	21
78	G0822 03	0.5	6.91	<5	695	<5	2.08	<1	2	82	31	1.58	1.31	<10	0.31	315	37	2.64	5	460	28	<5	<20	551	0.17	<10	23	<10	4	51
79	G0822 04	0.4	6.55	5	630	<5	1.90	<1	<1	114	36	1.73	1.33	<10	0.33	360	624	2.33	6	520	30	<5	<20	484	0.18	<10	25	<10	3	51
80	G0822 05	0.3	6.50	5	500	<5	1.95	<1	1	66	33	1.56	1.11	<10	0.32	317	477	2.30	4	470	28	<5	<20	485	0.17	30	25	120	3	45
81	G0822 06	0.6	7.08	10	975	<5	1.54	<1	5	21	149	2.76	2.85	30	0.59	622	682	1.68	17	850	34	<5	<20	332	0.25	<10	46	<10	16	90
82	G0822 07	0.4	6.06	5	525	<5	1.88	<1	<1	111	76	1.65	1.22	<10	0.30	337	740	2.19	5	520	28	<5	<20	465	0.17	30	25	60	2	54
83	G0822 08	0.4	6.33	10	480	<5	2.13	<1	<1	71	29	1.53	0.96	<10	0.33	338	53	2.33	5	470	26	<5	<20	492	0.17	<10	25	<10	2	47
84	G0822 09	0.5	6.71	10	1450	65	0.91	<1	<1	74	39	0.64	2.08	10	0.11	140	30	2.02	3	190	48	<5	<20	312	0.04	<10	5	<10	10	21
85	G0822 10	0.5	6.33	5	550	5	1.91	<1	<1	86	80	1.48	1.21	<10	0.28	312	83	2.64	4	450	28	<5	<20	470	0.16	<10	23	<10	4	41
86	G0822 11	0.7	5.34	5	520	<5	1.77	<1	<1	78	69	1.53	1.28	<10	0.26	279	270	2.44	5	350	26	<5	<20	390	0.16	<10	22	<10	3	43
87	G0822 12	0.3	6.00	5	600	<5	1.89	<1	<1	107	45	1.45	1.18	<10	0.26	281	242	2.44	5	390	26	<5	<20	452	0.15	<10	22	<10	3	46
88	G0822 13	0.6	6.38	5	765	<5	1.78	<1	1	103	64	1.54	1.37	<10	0.29	326	43	2.49	5	410	30	<5	<20	472	0.15	<10	24	<10	4	49
89	G0822 14	0.6	7.29	10	990	<5	1.20	<1	6	21	166	2.98	2.72	30	0.59	642	647	1.61	17	870	38	<5	<20	330	0.26	30	48	<10	16	99
90	G0822 15	0.5	6.55	5	745	<5	1.75	<1	<1	85	83	1.59	1.37	<10	0.28	299	178	2.45	4	420	30	<5	<20	454	0.14	<10	21	<10	5	49
91	G0822 16	0.3	5.99	<5	480	<5	2.01	<1	1	111	53	1.58	0.99	<10	0.30	287	156	2.43	6	410	26	<5	<20	453	0.17	<10	25	<10	2	48
92	G0822 17	0.5	6.42	5	655	15	1.72	<1	1	101	101	1.68	1.27	<10	0.32	347	225	2.43	5	360	32	<5	<20	469	0.16	<10	24	<10	4	47
93	G0822 18	0.4	6.55	10	620	<5	1.75	<1	1	107	33	1.59	1.30	<10	0.31	289	197	2.66	5	430	32	<5	<20	480	0.17	<10	27	50	4	45
94	G0822 19	0.2	6.37	10	545	<5	1.94	<1	1	87	50	1.57	1.12	<10	0.29	294	187	2.51	4	430	32	<5	<20	462	0.17	<10	25	<10	3	47
95	G0822 20	<0.2	6.87	5	485	<5	2.34	<1	1	98	60	1.86	1.05	<10	0.35	336	96	2.65	5	520	30	<5	<20	507	0.20	<10	29	<10	3	57
96	G0822 21	<0.2	6.82	5	565	<5	2.14	<1	1	90	56	1.90	1.19	<10	0.33	433	276	2.63	5	420	30	<5	<20	497	0.20	<10	27	<10	3	63
97	G0822 22	0.4	6.22	5	570	<5	1.97	<1	<1	121	71	1.75	1.20	<10	0.31	379	401	2.36	6	380	28	<5	<20	466	0.18	<10	27	<10	3	58
98	G0822 23	1.4	7.24	10	1310	<5	1.34	<1	<1	86	790	1.15	1.71	10	0.16	208	141	2.12	3	260	36	<5	<20	390	0.09	<10	14	<10	9	75
99	G0822 24	0.2	6.78	5	595	<5	2.09	<1	<1	107	42	1.87	1.38	<10	0.27	391	361	2.70	5	470	32	<5	<20	460	0.17	<10	23	<10	4	63
100	G0822 25	0.4	6.20	10	625	<5	1.39	<1	<1	92	53	1.74	1.31	<10	0.30	284	302	2.40	6	390	28	<5	<20	468	0.17	<10	28	<10	3	41
101	G0822 26	0.4	7.67	10	975	<5	1.84	<1	5	19	132	2.94	2.46	30	0.59	645	652	1.75	17	900	40	<5	<20	330	0.27	<10	46	<10	15	99
102	G0822 27	0.2	9.07	10	1200	<5	2.46	<1	2	54	186	2.36	1.17	<10	0.45	503	188	2.88	5	600	40	<5	<20	526	0.22	<10	25	<10	3	61
103	G0822 28	0.2	6.32	10	425	<5	2.21	<1	<1	104	31	1.88	0.96	<10	0.31	343	760	2.50	5	550	26	<5	<20	451	0.18	<10	26	<10	3	49
104	G0822 29	0.3	6.57	5	1005	<5	1.69	<1	<1	93	35	1.22	1.48	<10	0.23	208	80	2.35	5	350	30	<5	<20	432	0.12	<10	18	<10	6	32
105	G0822 30	<0.2	5.84	35	570	<5	2.01	<1	<1	98	108	1.62	1.19	<10	0.27	301	390	2.44	5	400	28	<5	<20	426	0.16	<10	24	<10	3	42

Et #.	Tag #	Ag	Al%	As	Ba	Bi	Ca%	Cd	Co	Cr	Cu	Fe%	K%	La	Mg%	Mn	Mo	Na%	Ni	P	Pb	Sb	Sn	Sr	Ti%	U	V	W	Y	Zn
106	G082231	<0.2	5.85	25	3235	<5	1.36	<1	1	109	78	1.54	1.39	<10	0.29	280	369	2.21	5	370	30	<5	<20	531	0.14	<10	23	<10	5	42
107	G082232	0.2	5.50	5	500	<5	1.30	<1	<1	106	53	1.58	1.05	<10	0.32	279	373	2.42	4	440	22	<5	<20	459	0.16	<10	24	<10	3	41
108	G082233	<0.2	6.07	5	510	<5	1.43	<1	1	132	70	1.96	1.07	<10	0.31	335	558	2.48	6	500	26	<5	<20	505	0.17	<10	25	<10	4	47
109	G082234	0.2	6.20	15	745	<5	1.32	<1	<1	119	117	1.31	1.94	10	0.18	209	3139	1.82	4	520	28	<5	<20	339	0.09	<10	12	<10	8	32
110	G082235	0.5	6.47	10	1165	5	1.02	<1	<1	81	33	0.53	2.83	20	0.07	93	107	1.66	2	180	36	<5	<20	250	0.03	<10	3	<10	10	14
111	G082236	0.4	7.45	10	860	<5	1.88	<1	6	22	132	3.00	2.72	30	0.57	665	672	1.66	18	950	34	<5	<20	322	0.27	<10	44	<10	16	100
112	G082237	<0.2	6.51	20	610	<5	1.96	<1	1	129	76	1.83	1.31	<10	0.33	300	368	2.14	6	450	22	<5	<20	488	0.17	<10	25	<10	3	43
113	G082238	0.2	6.26	5	485	<5	1.74	<1	1	136	77	1.86	1.01	<10	0.29	330	112	2.44	6	440	24	<5	<20	455	0.16	<10	26	<10	3	38
114	G082239	0.2	6.97	10	545	<5	1.65	<1	<1	124	172	2.17	1.10	<10	0.35	328	3011	2.52	6	570	26	<5	<20	550	0.18	<10	29	<10	3	44
115	G082240	<0.2	5.49	5	490	15	1.17	<1	<1	134	49	1.54	1.12	<10	0.30	254	6266	1.99	5	440	20	<5	<20	440	0.14	<10	23	<10	3	31
116	G082241	0.3	5.36	5	470	30	1.24	<1	<1	122	55	1.48	1.23	<10	0.28	244	3257	1.98	4	410	22	<5	<20	428	0.15	<10	24	<10	3	33
117	G082242	<0.2	6.12	<5	435	<5	2.05	<1	1	140	99	1.93	0.97	<10	0.34	274	284	2.50	5	480	22	<5	<20	529	0.18	<10	26	<10	3	37
118	G082243	<0.2	5.83	<5	405	<5	2.11	<1	2	125	169	2.04	0.95	<10	0.32	252	205	2.19	6	490	24	<5	<20	488	0.18	<10	24	<10	3	36
119	G082244	<0.2	6.47	5	560	<5	2.16	<1	1	117	88	1.85	1.12	<10	0.32	267	180	2.45	6	470	24	<5	<20	529	0.18	<10	25	<10	4	40
120	G082245	0.4	6.64	<5	950	<5	1.53	<1	<1	99	74	1.28	2.05	10	0.21	197	89	2.32	4	330	30	<5	<20	447	0.11	<10	15	<10	9	29
121	G082246	2.6	6.69	5	1205	245	1.25	2	1	101	955	1.16	2.55	10	0.16	156	12	2.25	4	270	62	<5	<20	399	0.08	<10	11	<10	9	80
122	G082247	0.5	6.90	15	890	<5	1.75	<1	6	21	131	2.80	2.96	30	0.57	620	634	1.61	17	890	36	<5	<20	319	0.25	<10	45	<10	16	95
123	G082248	0.5	6.19	5	510	<5	2.34	<1	2	114	292	1.68	0.90	<10	0.34	265	68	2.54	5	470	24	<5	<20	570	0.18	<10	24	<10	3	46
124	G082249	1.2	6.80	85	565	50	2.80	<1	2	114	399	1.64	0.97	<10	0.34	268	27	2.87	6	480	40	<5	<20	552	0.20	<10	26	<10	2	66
125	G082250	0.2	6.82	<5	545	<5	2.40	<1	1	106	42	1.51	0.81	<10	0.34	257	220	2.75	5	470	22	<5	<20	609	0.18	<10	24	<10	2	37
126	G082251	<0.2	6.33	5	560	<5	2.48	<1	2	124	27	1.39	0.73	<10	0.34	250	30	2.60	6	430	24	<5	<20	607	0.18	<10	24	<10	2	38
127	G082252	<0.2	7.02	5	620	<5	2.56	<1	2	88	22	1.49	0.80	<10	0.38	311	10	2.76	5	470	24	<5	<20	654	0.20	<10	26	<10	2	48
128	G082253	<0.2	6.61	5	580	<5	2.37	<1	2	119	73	1.68	0.89	<10	0.39	304	92	2.53	6	530	24	<5	<20	590	0.20	<10	28	<10	3	47
129	G082254	0.4	6.15	10	505	<5	2.03	<1	<1	115	107	1.72	0.89	<10	0.32	297	710	2.48	5	480	22	<5	<20	528	0.18	<10	27	<10	3	44
130	G082255	0.2	6.56	10	870	<5	1.68	<1	6	21	127	2.66	2.93	30	0.57	614	631	1.51	16	860	32	<5	<20	315	0.24	<10	44	<10	16	90
131	G082256	0.4	6.67	5	545	<5	2.54	<1	1	129	44	1.70	0.83	<10	0.38	348	52	2.67	6	530	24	<5	<20	622	0.20	<10	26	<10	3	46
132	G082257	0.3	6.78	10	850	<5	1.79	<1	6	21	128	2.75	2.78	30	0.56	634	634	1.59	18	880	32	<5	<20	321	0.25	<10	45	<10	15	93
133	G082258	0.3	6.63	<5	605	<5	2.16	<1	1	105	46	1.77	1.08	<10	0.39	351	141	2.37	6	490	22	<5	<20	569	0.19	<10	26	<10	3	44
134	G082259	<0.2	6.15	<5	580	<5	2.02	<1	1	122	58	1.66	1.01	<10	0.33	312	172	2.25	6	500	24	<5	<20	529	0.17	<10	24	<10	3	42
135	G082260	<0.2	7.87	10	1535	<5	1.76	<1	1	113	127	1.88	2.78	10	0.34	325	301	1.95	6	550	34	<5	<20	608	0.16	<10	25	20	5	43
136	G082261	<0.2	5.78	5	685	<5	1.29	<1	<1	137	88	1.84	1.26	<10	0.33	301	775	2.04	6	490	22	<5	<20	496	0.17	<10	28	<10	3	43
137	G082262	0.4	6.81	5	620	<5	2.28	<1	2	108	90	1.95	0.94	<10	0.38	323	221	2.36	6	570	24	<5	<20	580	0.19	<10	27	<10	3	47
138	G082263	0.3	6.32	5	585	<5	2.38	<1	2	111	34	1.57	0.81	<10	0.38	368	16	2.66	6	500	26	<5	<20	636	0.20	<10	27	<10	2	57
139	G082264	0.6	6.50	5	605	<5	2.39	<1	1	118	88	1.78	0.92	<10	0.37	388	67	2.54	6	510	24	<5	<20	606	0.19	<10	27	<10	2	53
140	G082265	0.4	6.58	10	885	<5	1.67	<1	5	22	132	2.64	2.99	30	0.58	596	648	1.52	16	840	30	<5	<20	315	0.24	<10	44	<10	15	86
141	G082266	0.2	6.78	5	605	<5	2.56	<1	2	120	39	1.62	0.77	<10	0.40	320	8	2.89	7	540	24	<5	<20	643	0.21	<10	33	<10	1	49
142	G082267	0.4	4.64	20	320	<5	1.42	<1	<1	197	107	1.31	0.70	<10	0.26	292	>10000	1.39	6	740	18	<5	<20	324	0.11	<10	19	<10	4	32
143	G082268	<0.2	6.63	165	425	<5	2.10	<1	1	103	34	1.65	0.97	<10	0.33	351	55	2.40	6	540	24	<5	<20	532	0.20	<10	29	<10	2	64
144	G082269	<0.2	7.25	15	590	<5	2.34	<1	2	124	19	1.64	0.99	<10	0.33	358	127	2.57	6	450	26	<5	<20	603	0.18	<10	25	<10	2	65
145	G082270	<0.2	6.93	5	570	<5	1.71	<1	1	109	14	1.74	0.79	<10	0.35	441	214	2.57	6	500	26	<5	<20	616	0.19	<10	28	<10	2	79
146	G082271	0.2	6.50	5	560	<5	1.92	<1	2	105	63	1.72	0.87	<10	0.33	389	127	2.26	6	460	26	<5	<20	551	0.17	<10	26	<10	2	70

Et #.	Tag #	Ag	Al%	As	Ba	Bi	Ca%	Cd	Co	Cr	Cu	Fe%	K%	La	Mg%	Mn	Mo	Na%	Ni	P	Pb	Sb	Sn	Sr	Ti%	U	V	W	Y	Zn	
QC DATA:																															
<i>Repeat:</i>																															
1	G082126	0.4	5.83	100	1530	<5	0.73	1	<1	40	17	0.47	3.40	10	0.05	81	474	1.46	5	260	32	<5	<20	228	0.03	<10	4	<10	9	84	
10	G082135	<0.2	6.60	<5	585	<5	2.05	<1	1	45	8	1.91	1.41	<10	0.33	362	149	2.12	4	630	26	<5	<20	461	0.18	<10	22	<10	5	62	
19	G082144	0.3	6.22	30	555	<5	2.10	<1	2	97	35	2.16	1.46	<10	0.36	427	136	2.00	6	620	36	<5	<20	431	0.20	<10	24	<10	3	74	
36	G082161	0.6	6.58	15	1420	<5	0.71	<1	<1	73	50	0.65	3.45	10	0.05	87	94	2.05	3	150	44	<5	<20	216	0.03	<10	3	<10	8	43	
45	G082170	0.5	7.13	<5	760	<5	1.94	<1	1	98	32	1.96	1.42	<10	0.27	361	73	2.28	5	400	32	<5	<20	508	0.15	<10	19	<10	4	64	
54	G082179	0.8	6.68	5	1105	<5	1.56	<1	<1	73	23	1.16	2.29	<10	0.24	210	38	2.32	4	320	36	<5	<20	446	0.12	<10	15	<10	6	43	
71	G082196	0.5	6.15	<5	445	<5	2.02	<1	1	71	27	1.53	0.98	<10	0.31	280	42	2.54	4	440	26	<5	<20	520	0.18	<10	24	<10	2	41	
80	G082205	0.4	6.53	5	480	10	2.00	<1	1	62	29	1.65	1.16	<10	0.31	323	490	2.63	5	480	30	<5	<20	477	0.18	<10	27	110	3	48	
106	G082231	<0.2	6.20	25	3260	<5	1.37	<1	<1	107	79	1.58	1.42	<10	0.30	282	337	2.24	6	370	30	<5	<20	550	0.15	<10	23	<10	5	41	
115	G082240	<0.2	5.74	10	495	20	1.70	<1	<1	136	49	1.58	1.11	<10	0.30	264	5910	2.08	5	460	24	<5	<20	436	0.15	<10	21	<10	3	33	
124	G082249	1.2	6.51	80	575	45	2.07	<1	2	115	408	1.62	0.94	<10	0.34	267	27	2.65	6	480	42	<5	<20	556	0.19	<10	26	<10	2	72	
141	G082266	<0.2	7.08	10	630	<5	2.52	<1	2	120	38	1.62	0.76	<10	0.40	326	8	2.75	6	540	24	<5	<20	679	0.20	<10	33	<10	2	49	
<i>Respiit:</i>																															
1	G082126	0.3	5.88	100	1450	<5	0.69	1	<1	44	16	0.51	2.89	10	0.06	102	459	1.36	2	250	34	<5	<20	248	0.05	<10	3	<10	9	82	
36	G082161	0.4	6.52	25	1490	<5	0.69	<1	<1	45	55	0.57	3.20	20	0.05	75	95	1.96	2	140	36	<5	<20	227	0.02	<10	2	<10	8	36	
71	G082196	0.5	6.30	5	435	<5	2.16	<1	1	99	27	1.56	1.00	<10	0.31	278	45	2.67	6	420	30	<5	<20	471	0.17	<10	25	<10	2	40	
106	G082231	<0.2	5.85	20	3265	<5	2.10	<1	<1	109	92	1.69	1.17	<10	0.32	290	371	2.40	5	400	28	<5	<20	575	0.16	<10	22	<10	4	45	
141	G082266	0.2	7.10	5	630	<5	2.62	<1	1	116	42	1.58	0.72	<10	0.39	326	6	2.65	7	560	26	<5	<20	675	0.20	<10	28	<10	2	47	
<i>Standard:</i>																															
STSD - 3		0.5	5.55	25	1460	<5	2.40	<1	17	60	40	4.03	1.40	30	1.29	2669	6	1.09	33	1660	56	<5	<20	247	0.35	<10	109	<10	31	217	
STSD - 3		0.6	5.72	25	1475	<5	2.60	1	17	64	45	4.39	1.26	40	1.43	2608	6	1.11	33	1720	58	<5	<20	281	0.36	<10	126	<10	34	216	
STSD - 3		0.6	5.88	25	1430	<5	2.51	<1	17	63	42	4.22	1.39	40	1.31	2583	7	1.10	32	1690	56	<5	<20	266	0.35	<10	122	<10	33	207	
STSD - 3		0.5	5.66	25	1400	<5	2.42	1	17	60	41	4.21	1.28	40	1.29	2616	6	1.05	31	1670	56	<5	<20	261	0.33	<10	110	<10	33	206	
STSD - 3		0.6	5.82	25	1410	<5	2.46	1	17	62	42	4.17	1.39	30	1.30	2535	6	1.09	32	1660	54	<5	<20	263	0.34	<10	118	<10	32	205	

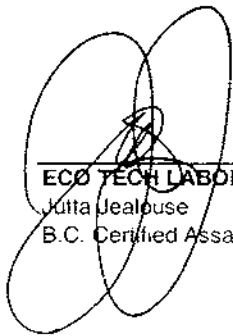
ECO TECH LABORATORY LTD.
 Jutta Jealouse
 B.C. Certified Assayer

JJ/ml
 d:\d1316a\S4d1316bS
 XLS/07

ECO TECH LABORATORY LTD.

10041 Dallas Drive
KAMLOOPS, B.C.
V2C 6T4

ICP CERTIFICATE OF ANALYSIS AK 2007- 1264

Pacific Cascade Resources

520 - 700 W. Pender Street
Vancouver, BC
V6C 1G8

Phone: 250-573-5700

Fax : 250-573-4557

No. of samples received: 125

Sample Type: Core

Project: Cracis Moly

Submitted by: Pacific Cascade Resources

Values in ppm unless otherwise reported

Et #.	Tag #	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	K %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
1	G082001	0.4	5.76	<5	585	<5	2.07	1	2	87	59	1.71	0.91	<10	0.36	348	18	2.40	6	530	20	<5	<20	486	0.20	<10	25	<10	2	99
2	G082002	0.4	6.28	5	605	<5	2.01	<1	2	120	116	1.73	0.90	<10	0.35	360	62	2.26	6	490	22	<5	<20	484	0.18	<10	25	<10	2	69
3	G082003	0.6	6.10	10	615	10	2.24	<1	2	97	169	1.56	0.80	<10	0.37	326	34	2.45	5	490	22	<5	<20	545	0.20	<10	23	<10	2	64
4	G082004	0.4	7.39	10	665	<5	2.72	<1	3	92	16	1.86	0.86	<10	0.41	360	22	2.73	6	570	26	<5	<20	659	0.22	<10	27	<10	2	85
5	G082005	0.4	7.44	10	645	<5	2.04	<1	3	92	153	2.18	1.26	<10	0.41	429	23	2.45	6	630	24	<5	<20	583	0.20	<10	25	<10	3	122
6	G082006	0.2	6.49	<5	495	<5	2.08	<1	3	132	1728	2.79	0.88	<10	0.35	325	160	2.11	7	550	24	<5	<20	491	0.19	<10	22	<10	2	88
7	G082007	<0.2	6.72	5	620	<5	2.31	<1	2	110	55	1.66	0.87	<10	0.41	327	56	2.63	6	510	20	<5	<20	589	0.21	<10	27	<10	2	70
8	G082008	<0.2	6.80	5	590	<5	2.80	<1	3	78	18	1.61	0.83	<10	0.40	319	24	2.75	6	570	24	<5	<20	580	0.22	<10	29	<10	2	65
9	G082009	<0.2	6.63	15	525	<5	2.61	2	2	78	23	1.54	0.80	<10	0.35	342	22	2.66	6	520	24	<5	<20	544	0.21	<10	26	<10	2	104
10	G082010	<0.2	7.67	10	915	<5	1.90	<1	5	22	135	2.92	2.94	30	0.62	705	661	1.68	18	970	38	<5	<20	356	0.27	<10	47	<10	16	101
11	G082011	0.2	6.11	5	480	<5	2.19	<1	2	89	62	1.68	1.00	<10	0.33	395	63	2.33	6	490	22	<5	<20	429	0.19	<10	25	<10	2	62
12	G082012	0.2	6.26	<5	465	<5	2.40	<1	2	84	55	1.63	0.90	<10	0.36	314	54	2.35	5	480	24	<5	<20	495	0.19	<10	26	<10	2	71
13	G082013	0.2	6.49	5	535	<5	2.12	<1	2	114	33	1.72	0.95	<10	0.38	318	100	2.45	6	550	22	<5	<20	513	0.22	<10	26	<10	2	70
14	G082014	<0.2	6.48	<5	535	<5	2.65	<1	1	97	2	1.62	0.76	<10	0.41	302	524	2.73	7	510	22	<5	<20	578	0.22	<10	27	<10	2	46
15	G082015	<0.2	6.64	5	530	<5	2.58	<1	2	115	17	1.68	0.83	<10	0.39	305	362	2.80	6	510	24	<5	<20	574	0.22	<10	27	<10	2	57
16	G082016	<0.2	6.65	<5	505	<5	2.46	<1	2	83	13	1.66	0.81	<10	0.38	309	104	2.63	5	510	22	<5	<20	558	0.21	<10	29	<10	2	54
17	G082017	<0.2	6.57	<5	595	<5	2.60	4	2	138	76	1.75	0.92	<10	0.39	334	35	2.72	7	540	22	<5	<20	565	0.21	<10	27	<10	2	165
18	G082018	<0.2	6.61	<5	570	<5	2.60	1	2	86	36	1.69	0.89	<10	0.42	338	89	2.74	6	520	22	<5	<20	595	0.21	<10	27	<10	2	77
19	G082019	0.4	6.42	<5	590	<5	2.55	<1	2	112	120	1.84	1.01	<10	0.40	365	202	2.59	6	560	20	<5	<20	562	0.21	<10	26	<10	2	68
20	G082020	0.2	6.66	5	580	<5	2.38	<1	2	86	133	1.79	1.15	<10	0.34	303	210	2.47	5	520	20	<5	<20	466	0.20	<10	27	<10	2	82
21	G082021	1.2	6.46	5	575	<5	2.14	2	2	142	632	1.89	1.14	<10	0.37	328	381	2.00	6	520	20	<5	<20	401	0.18	<10	26	<10	2	107
22	G082022	0.2	6.55	<5	575	<5	2.62	<1	2	84	16	1.75	0.91	<10	0.38	304	185	2.91	6	510	22	<5	<20	554	0.21	<10	28	<10	2	58
23	G082023	0.2	7.61	10	940	<5	1.93	<1	6	22	133	2.96	2.94	30	0.62	682	656	1.77	18	930	34	<5	<20	332	0.26	<10	44	<10	16	102
24	G082024	<0.2	6.49	<5	560	<5	2.36	<1	2	101	42	1.68	0.89	<10	0.37	319	254	2.56	5	500	22	<5	<20	530	0.19	<10	26	<10	2	51
25	G082025	<0.2	6.47	5	665	<5	2.21	1	2	82	55	1.71	1.02	<10	0.38	375	55	2.71	6	500	24	<5	<20	529	0.20	<10	28	<10	2	93

Et #.	Tag #	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	K %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
26	G082026	0.4	6.76	10	700	<5	2.42	1	2	146	96	1.98	1.20	<10	0.36	403	98	2.70	6	500	24	<5	<20	526	0.20	<10	27	<10	2	88
27	G082027	1.0	7.38	15	775	<5	1.83	14	3	86	289	2.55	1.79	<10	0.30	428	63	2.03	5	470	26	<5	<20	414	0.16	<10	23	<10	4	528
28	G082028	2.8	6.71	280	1210	10	0.59	11	2	95	1580	1.53	2.45	10	0.08	174	66	1.61	4	200	30	10	<20	199	0.02	<10	3	<10	15	339
29	G082029	1.0	6.78	65	1160	5	0.49	4	2	65	287	1.32	2.53	10	0.08	197	81	1.19	3	160	32	<5	<20	133	0.02	<10	2	<10	14	154
30	G082030	0.6	6.51	30	1060	10	0.51	4	3	84	522	2.11	2.46	10	0.08	269	103	1.19	3	190	26	<5	<20	122	0.02	<10	1	<10	18	173
31	G082031	1.0	6.66	10	1225	20	0.37	6	3	70	548	1.85	2.72	10	0.06	248	108	1.43	3	170	30	<5	<20	136	0.02	<10	2	<10	17	148
32	G082032	0.6	7.03	10	1390	10	0.50	15	1	75	220	1.02	2.85	10	0.07	186	66	1.97	3	160	32	<5	<20	165	0.02	<10	1	<10	17	379
33	G082033	0.2	9.89	10	1115	<5	2.61	<1	2	23	140	2.12	2.80	<10	0.50	496	177	3.31	3	710	38	<5	<20	615	0.21	<10	24	<10	4	65
34	G082034	0.4	6.38	10	1380	<5	0.48	35	<1	67	107	0.90	2.67	10	0.05	173	29	2.36	2	140	32	<5	<20	139	0.02	<10	<1	<10	16	746
35	G082035	0.4	7.35	5	1495	<5	0.67	3	1	64	109	0.91	2.73	10	0.06	197	38	2.32	2	140	36	<5	<20	173	0.02	<10	1	<10	17	83
36	G082036	0.4	7.19	5	1425	<5	1.01	3	1	58	102	1.04	2.58	10	0.12	198	58	2.46	2	210	34	<5	<20	355	0.05	<10	7	<10	16	150
37	G082037	0.8	7.31	15	610	5	2.13	<1	3	77	103	1.83	0.98	<10	0.37	326	43	2.74	6	530	24	<5	<20	550	0.19	<10	29	<10	2	64
38	G082038	0.4	7.17	5	655	<5	2.41	<1	2	102	37	1.78	0.93	<10	0.41	349	64	2.76	5	530	24	<5	<20	598	0.21	<10	30	<10	2	61
39	G082039	0.4	6.86	5	725	<5	2.07	8	2	62	73	1.51	1.21	<10	0.34	343	15	2.49	5	430	26	<5	<20	521	0.16	<10	24	<10	5	239
40	G082040	0.4	6.59	5	855	10	1.92	7	2	96	58	1.37	1.22	<10	0.31	257	138	2.56	4	410	26	<5	<20	540	0.15	<10	23	<10	5	223
41	G082041	0.2	8.11	10	890	<5	1.98	<1	7	22	133	2.98	3.01	30	0.61	677	663	1.96	18	960	34	<5	<20	342	0.27	<10	45	<10	16	99
42	G082042	0.2	7.31	5	2000	<5	1.09	<1	1	58	69	1.13	3.14	<10	0.18	206	177	1.48	3	390	28	<5	<20	402	0.08	<10	10	<10	11	41
43	G082043	0.4	6.62	5	2555	<5	0.37	<1	1	60	77	0.86	3.57	10	0.11	114	44	0.74	2	160	24	<5	<20	235	0.02	<10	7	<10	14	53
44	G082044	0.4	6.98	10	610	<5	2.42	<1	2	66	62	1.86	1.26	<10	0.42	357	82	2.68	6	600	26	<5	<20	540	0.20	<10	32	<10	3	47
45	G082045	0.4	6.34	5	535	<5	2.22	<1	2	91	10	1.68	0.91	<10	0.38	330	30	2.55	6	460	22	<5	<20	529	0.20	<10	30	<10	2	53
46	G082046	0.4	6.75	10	525	<5	2.49	<1	2	71	68	1.77	1.02	<10	0.39	346	19	2.76	5	520	24	<5	<20	547	0.20	<10	27	<10	2	74
47	G082047	0.4	7.25	10	650	<5	2.66	<1	2	107	18	1.73	0.92	<10	0.41	349	56	3.02	5	540	22	<5	<20	636	0.21	<10	29	<10	2	64
48	G082048	0.2	6.57	<5	460	<5	2.58	<1	1	86	16	1.57	0.78	<10	0.37	314	505	2.90	5	520	22	<5	<20	535	0.21	<10	28	<10	2	76
49	G082049	0.4	7.28	15	830	<5	2.10	1	2	75	33	1.64	1.45	<10	0.39	416	66	2.29	4	510	22	<5	<20	492	0.19	<10	28	<10	3	99
50	G082050	0.6	6.66	5	590	<5	2.18	<1	2	79	173	1.86	0.98	<10	0.40	398	90	2.60	5	530	22	<5	<20	525	0.19	<10	29	<10	2	58
51	G082051	0.8	6.96	10	560	<5	2.10	<1	2	101	175	2.21	1.34	<10	0.37	415	46	2.35	6	580	22	<5	<20	467	0.20	<10	33	<10	2	65
52	G082052	0.6	6.75	35	495	<5	1.98	1	2	77	53	1.87	1.28	<10	0.36	361	116	2.19	5	510	24	<5	<20	466	0.18	<10	27	<10	2	95
53	G082053	0.4	8.05	15	625	5	2.34	<1	2	82	30	2.10	1.69	<10	0.42	401	68	2.13	6	540	24	<5	<20	492	0.21	<10	30	<10	3	89
54	G082054	0.2	6.47	5	500	<5	2.30	<1	2	97	16	1.83	1.06	<10	0.38	382	39	2.63	6	490	20	<5	<20	543	0.20	<10	29	<10	2	62
55	G082055	0.2	6.84	5	445	<5	2.25	<1	2	71	47	2.16	1.25	<10	0.40	439	34	2.73	6	530	22	<5	<20	531	0.20	<10	28	<10	2	77
56	G082056	0.2	7.38	10	905	<5	1.80	<1	6	21	135	2.83	2.67	30	0.59	636	644	1.87	17	880	30	<5	<20	331	0.25	<10	45	<10	15	96
57	G082057	0.2	9.20	10	1140	<5	2.85	<1	3	35	99	2.26	2.66	<10	0.45	512	155	2.85	4	600	34	<5	<20	551	0.22	<10	21	<10	3	73
58	G082058	0.6	7.95	10	735	<5	2.06	3	2	70	111	2.57	1.82	<10	0.42	513	114	2.15	6	590	26	<5	<20	495	0.21	<10	30	<10	3	284
59	G082059	0.4	7.71	25	725	<5	2.06	<1	2	86	84	2.43	1.70	<10	0.40	471	170	1.98	6	600	22	<5	<20	467	0.20	<10	28	<10	3	104
60	G082060	0.4	7.02	5	605	<5	2.30	<1	2	69	10	1.87	1.15	<10	0.40	332	52	2.49	5	540	22	<5	<20	549	0.21	<10	29	<10	2	59
61	G082061	0.2	6.68	5	560	<5	2.35	<1	2	101	10	1.98	0.98	<10	0.35	389	29	2.71	6	530	22	<5	<20	544	0.21	<10	27	<10	2	71
62	G082062	0.6	5.97	<5	515	<5	1.96	1	2	68	44	2.12	1.30	<10	0.36	412	81	2.42	5	540	20	<5	<20	454	0.19	<10	27	<10	3	112
63	G082063	0.4	6.37	5	1170	<5	1.11	1	1	118	70	1.35	2.17	10	0.18	209	107	1.75	4	260	24	<5	<20	355	0.07	<10	10	<10	8	77
64	G082064	0.4	6.66	75	510	<5	1.88	1	2	77	99	2.15	1.28	<10	0.31	377	99	2.39	5	460	24	<5	<20	448	0.15	<10	21	<10	4	93
65	G082065	0.2	6.79	10	460	<5	1.94	1	2	118	46	2.22	1.28	<10	0.31	456	51	2.37	6	560	22	<5	<20	428	0.20	<10	29	<10	2	117

El #.	Tag #	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	K %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
66	G082066	<0.2	8.03	10	905	<5	1.59	<1	2	73	37	2.60	2.12	<10	0.33	608	113	2.10	5	490	26	<5	<20	424	0.16	<10	21	<10	6	143
67	G082067	<0.2	7.22	5	590	<5	1.84	<1	2	109	89	2.21	1.47	<10	0.34	470	75	2.52	5	490	24	<5	<20	483	0.17	<10	24	<10	4	85
68	G082068	0.2	6.92	<5	535	<5	1.70	<1	1	67	21	1.62	1.33	<10	0.24	410	42	2.30	4	360	22	<5	<20	444	0.12	<10	18	<10	7	68
69	G082069	0.2	7.41	10	900	<5	1.85	<1	6	22	132	2.93	2.99	30	0.58	640	642	1.84	17	900	32	<5	<20	327	0.26	<10	46	<10	16	94
70	G082070	<0.2	6.92	5	550	<5	1.66	<1	2	97	41	2.23	1.66	<10	0.29	409	48	2.07	5	460	28	<5	<20	385	0.15	<10	20	<10	5	80
71	G082071	0.4	7.36	10	505	<5	1.83	<1	2	79	23	2.37	1.60	10	0.30	560	63	2.35	5	470	22	<5	<20	436	0.16	<10	23	<10	5	108
72	G082072	0.2	7.77	10	565	<5	1.72	<1	2	90	85	2.90	1.66	<10	0.34	674	188	2.42	6	500	24	<5	<20	464	0.18	<10	25	<10	4	165
73	G082073	0.2	7.23	80	515	<5	1.13	5	1	97	218	2.92	1.76	<10	0.27	475	741	1.67	6	510	24	<5	<20	314	0.15	<10	20	<10	4	438
74	G082074	0.2	6.64	<5	1340	<5	0.70	6	<1	78	103	1.01	3.16	10	0.08	106	46	1.56	4	170	30	<5	<20	273	0.04	<10	4	<10	10	414
75	G082075	0.2	6.49	10	1390	<5	0.86	<1	<1	58	36	0.78	3.23	20	0.07	114	157	1.28	3	180	30	<5	<20	236	0.03	<10	2	<10	9	59
76	G082076	0.2	6.54	30	1465	<5	0.80	1	<1	65	54	0.70	3.54	20	0.05	80	49	1.50	3	160	34	<5	<20	239	0.03	<10	<1	<10	9	83
77	G082077	0.4	5.84	45	1290	<5	0.58	<1	<1	56	32	0.51	3.13	10	0.04	60	48	1.27	2	130	30	<5	<20	219	0.02	<10	2	<10	7	29
78	G082078	0.2	5.53	55	995	<5	0.62	3	<1	90	55	0.68	2.60	10	0.06	65	89	1.30	3	150	22	<5	<20	192	0.02	<10	3	<10	7	115
79	G082079	0.2	7.71	10	895	<5	1.85	<1	6	21	131	2.89	3.09	30	0.58	652	649	1.69	17	920	32	<5	<20	334	0.27	<10	47	<10	16	93
80	G082080	0.2	6.94	10	540	<5	1.95	1	1	71	43	1.72	1.33	<10	0.29	302	93	2.38	5	410	22	<5	<20	459	0.15	<10	23	<10	5	109
81	G082081	0.4	6.76	10	1445	<5	1.32	4	1	73	32	0.95	2.48	10	0.15	200	41	2.39	3	240	30	<5	<20	408	0.08	<10	10	<10	11	165
82	G082082	0.2	6.74	<5	425	<5	2.48	<1	2	72	25	1.85	1.07	<10	0.37	420	76	2.78	5	510	22	<5	<20	520	0.20	<10	29	<10	3	76
83	G082083	0.4	6.41	160	1180	<5	0.90	4	<1	71	48	0.73	2.61	10	0.07	102	23	1.53	3	140	28	10	<20	220	0.03	<10	4	<10	10	145
84	G082084	0.4	7.68	10	635	<5	2.07	<1	2	62	105	2.41	1.71	<10	0.32	399	45	2.43	7	550	22	<5	<20	441	0.17	<10	24	<10	5	66
85	G082085	0.2	6.49	10	895	<5	1.17	<1	<1	72	31	1.01	2.11	10	0.12	190	73	2.27	3	210	26	<5	<20	287	0.06	<10	8	<10	12	43
86	G082086	0.2	6.76	5	1185	<5	1.05	2	1	63	65	1.27	2.77	10	0.14	190	53	2.00	3	260	28	<5	<20	276	0.07	<10	8	<10	10	114
87	G082087	0.4	5.95	10	1495	<5	0.73	<1	<1	64	48	0.70	3.16	10	0.05	81	127	1.50	2	140	28	<5	<20	257	0.03	<10	3	<10	10	41
88	G082088	0.2	6.16	20	1245	<5	0.90	<1	<1	60	28	0.95	2.71	10	0.09	169	80	2.38	3	190	28	<5	<20	236	0.05	<10	5	<10	11	33
89	G082089	0.4	6.53	40	1485	<5	0.74	<1	<1	62	46	0.73	2.96	10	0.07	132	38	2.21	3	160	32	<5	<20	263	0.03	<10	4	<10	12	35
90	G082090	0.4	6.67	5	605	<5	1.96	<1	2	86	57	2.23	1.45	<10	0.34	479	76	2.38	6	520	22	<5	<20	455	0.18	<10	25	<10	3	87
91	G082091	0.4	7.04	10	1485	<5	0.64	<1	<1	61	19	0.51	3.51	20	0.05	88	45	2.00	2	150	34	<5	<20	247	0.02	<10	2	<10	10	25
92	G082092	0.4	6.04	10	1405	<5	0.55	<1	<1	48	24	0.58	3.28	20	0.05	118	143	1.87	2	170	36	<5	<20	207	0.03	<10	2	<10	9	38
93	G082093	0.4	6.56	15	1405	<5	0.72	<1	<1	57	33	0.56	3.36	20	0.04	83	24	1.91	3	140	36	<5	<20	209	0.02	<10	1	<10	9	51
94	G082094	0.4	6.76	45	1400	<5	0.69	<1	<1	51	53	0.65	3.34	20	0.04	92	65	2.13	2	150	36	<5	<20	212	0.02	<10	1	<10	10	33
95	G082095	0.3	8.13	10	905	<5	1.95	<1	6	21	135	3.05	3.04	30	0.60	689	662	1.84	19	980	36	<5	<20	341	0.29	<10	48	<10	16	102
96	G082096	0.2	6.16	10	1345	<5	0.76	<1	<1	53	30	0.59	3.35	20	0.06	95	21	2.07	2	170	34	<5	<20	196	0.03	<10	1	<10	9	34
97	G082097	0.4	5.45	20	1180	20	0.71	2	<1	49	56	0.64	2.93	20	0.05	115	57	1.86	2	160	34	<5	<20	178	0.02	<10	2	<10	9	89
98	G082098	0.2	6.09	10	1485	<5	0.67	<1	<1	56	23	0.46	3.62	20	0.04	72	16	1.90	2	140	32	<5	<20	242	0.02	<10	<1	<10	9	19
99	G082099	0.4	6.48	10	1545	<5	0.67	<1	<1	45	20	0.46	3.40	20	0.04	66	30	1.96	2	150	34	<5	<20	253	0.02	<10	2	<10	10	31
100	G082100	0.4	6.44	95	1245	<5	0.64	1	<1	50	30	0.49	3.07	20	0.04	85	15	2.03	3	140	34	<5	<20	208	0.02	<10	<1	<10	9	42
101	G082101	0.6	6.97	200	1285	<5	0.46	2	<1	38	45	0.53	2.77	20	0.06	66	17	2.03	3	150	34	<5	<20	211	0.02	<10	1	<10	9	39
102	G082102	0.6	5.04	180	555	<5	1.26	2	<1	74	31	0.55	2.02	10	0.06	93	24	0.99	4	110	22	<5	<20	119	0.02	<10	2	<10	10	39
103	G082103	1.2	5.25	210	605	<5	0.75	2	<1	69	57	0.66	2.08	10	0.09	106	1627	1.04	3	120	24	<5	<20	109	0.02	<10	6	<10	8	32
104	G082104	0.4	4.64	100	910	<5	0.60	1	<1	92	85	0.59	2.33	10	0.03	59	108	1.16	3	100	24	<5	<20	156	0.01	<10	2	<10	7	47
105	G082105	0.6	5.86	100	1340	<5	0.79	3	<1	57	96	0.80	3.19	10	0.06	128	1860	1.77	3	160	30	<5	<20	195	0.03	<10	2	<10	8	140

Et #.	Tag #	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	K %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
106	G082106	0.2	6.17	15	1415	<5	0.76	<1	<1	71	28	0.59	2.97	20	0.05	113	106	1.53	3	170	44	<5	<20	218	0.03	<10	1	<10	9	72
107	G082107	0.4	6.69	20	1440	5	0.63	<1	<1	68	35	0.74	2.86	20	0.04	117	37	1.73	2	190	48	<5	<20	231	0.03	<10	2	<10	9	49
108	G082108	0.2	6.10	20	1415	<5	0.88	1	<1	66	31	0.60	2.84	20	0.05	103	27	1.80	2	170	34	<5	<20	247	0.03	<10	2	<10	11	46
109	G082109	0.2	7.10	10	895	<5	1.66	<1	6	22	129	2.73	2.83	30	0.58	634	671	1.38	17	900	34	<5	<20	358	0.26	<10	48	<10	16	100
110	G082110	0.2	9.89	10	1150	<5	2.32	<1	2	34	121	2.27	2.56	<10	0.47	555	206	2.96	5	750	42	<5	<20	628	0.23	<10	24	<10	4	83
111	G082111	0.4	6.10	10	1375	<5	0.78	1	<1	51	46	0.61	3.45	20	0.04	83	26	1.72	2	130	32	<5	<20	215	0.02	<10	3	<10	10	116
112	G082112	0.2	6.45	20	1440	<5	0.78	<1	<1	75	20	0.56	3.31	10	0.04	81	176	1.69	2	140	36	<5	<20	204	0.02	<10	4	<10	8	54
113	G082113	0.8	6.29	70	1115	15	0.86	5	<1	46	27	0.48	3.18	20	0.03	64	53	2.00	2	130	40	<5	<20	191	0.02	<10	4	<10	9	159
114	G082114	5.2	5.35	225	600	220	0.49	13	<1	113	213	1.05	2.11	10	0.06	99	88	1.57	4	140	110	20	<20	125	0.02	<10	7	<10	7	275
115	G082115	0.2	6.32	40	1240	<5	0.53	1	<1	49	25	0.58	3.55	20	0.04	107	45	1.92	2	150	34	<5	<20	194	0.03	<10	7	<10	9	61
116	G082116	0.2	6.21	35	1350	5	0.69	<1	<1	80	35	0.55	3.34	20	0.04	89	40	1.75	2	140	32	<5	<20	228	0.02	<10	8	<10	8	40
117	G082117	0.2	6.13	25	1280	5	0.56	<1	<1	47	26	0.50	3.47	20	0.04	81	32	1.96	1	130	32	<5	<20	204	0.02	<10	8	<10	9	35
118	G082118	0.2	8.46	5	995	<5	1.90	<1	<1	40	94	1.75	2.04	<10	0.30	286	173	3.16	3	510	26	<5	<20	561	0.17	<10	25	<10	2	37
119	G082119	<0.2	6.20	25	1290	<5	0.46	<1	<1	49	27	0.50	3.57	20	0.03	66	43	1.83	1	130	28	<5	<20	196	0.02	<10	9	<10	9	36
120	G082120	0.2	6.36	20	1305	<5	0.52	1	<1	70	52	0.65	3.41	20	0.04	76	33	1.98	1	140	32	<5	<20	210	0.02	<10	10	<10	9	45
121	G082121	0.2	6.57	35	1370	<5	0.41	3	<1	46	39	0.58	3.67	20	0.03	55	75	2.16	1	130	32	<5	<20	206	0.02	<10	11	<10	9	113
122	G082122	0.2	5.86	30	1265	<5	0.69	1	<1	74	39	0.63	3.49	20	0.04	92	85	1.99	2	150	30	<5	<20	215	0.03	<10	15	<10	9	43
123	G082123	0.2	5.82	20	1415	<5	0.55	1	<1	62	23	0.51	3.89	20	0.04	87	28	1.93	1	140	30	<5	<20	240	0.03	<10	13	<10	8	48
124	G082124	0.2	5.59	15	1420	<5	0.65	2	<1	81	29	0.53	3.55	20	0.05	101	97	1.88	1	150	30	5	<20	251	0.03	<10	14	<10	9	84
125	G082125	0.2	5.83	30	1470	<5	0.57	3	<1	55	45	0.60	3.88	20	0.04	78	198	2.10	<1	160	32	5	<20	254	0.03	<10	18	<10	9	115

QC DATA:**Repeat:**

1	G082001	0.4	5.80	<5	560	<5	2.10	1	2	89	58	1.80	0.92	<10	0.37	356	19	2.37	7	560	20	<5	<20	516	0.21	<10	27	<10	2	109
10	G082010	0.2	7.60	10	970	<5	1.87	<1	6	22	133	2.98	2.70	30	0.60	681	681	1.85	17	930	32	<5	<20	333	0.27	<10	45	<10	16	97
19	G082019	0.2	6.84	5	645	<5	2.55	<1	2	108	121	1.91	0.98	<10	0.40	347	207	2.58	5	530	22	<5	<20	569	0.22	<10	28	<10	2	74
36	G082036	0.2	7.19	10	1455	<5	1.09	3	2	60	103	1.06	2.50	10	0.12	196	54	2.35	3	220	34	<5	<20	359	0.05	<10	7	<10	16	148
45	G082045	0.2	6.26	<5	515	<5	2.32	<1	2	92	11	1.69	0.90	<10	0.37	317	27	2.73	6	480	22	<5	<20	548	0.20	<10	30	<10	2	53
54	G082054	0.2	6.50	5	485	<5	2.18	<1	2	93	16	1.86	1.00	<10	0.39	390	39	2.62	6	510	20	<5	<20	518	0.20	<10	28	<10	2	62
71	G082071	0.4	7.75	10	555	<5	1.86	<1	2	85	23	2.42	1.64	<10	0.32	568	67	2.43	5	480	26	<5	<20	480	0.16	<10	23	<10	5	107
80	G082080	0.2	6.98	10	540	<5	2.04	1	1	70	41	1.75	1.30	<10	0.29	308	95	2.39	5	420	22	<5	<20	447	0.16	<10	23	<10	5	111
89	G082089	0.4	6.53	40	1475	<5	0.71	<1	<1	63	44	0.68	2.94	10	0.06	135	37	2.06	2	150	32	<5	<20	273	0.03	<10	4	<10	12	32
106	G082106	0.2	6.67	10	1315	<5	0.62	<1	<1	62	29	0.61	3.52	20	0.03	91	109	1.80	2	140	38	<5	<20	217	0.02	<10	5	<10	9	60
115	G082115	0.2	5.69	40	1210	<5	0.51	1	<1	51	27	0.56	3.63	20	0.04	111	42	2.06	<1	140	34	5	<20	185	0.02	<10	14	<10	8	61

Resplit:


1	G082001	0.6	5.63	5	585	<5	2.11	<1	2	88	57	1.74	1.00	<10	0.40	342	20	2.42	5	530	22	<5	<20	490	0.20	<10	25	<10	2	91
36	G082036	0.2	6.76	10	1390	<5	1.01	3	2	75	97	1.02	2.56	10	0.13	185	53	2.41	3	210	32	<5	<20	372	0.06	<10	8	<10	16	146
71	G082071	0.4	7.12	10	520	<5	1.76	<1	2	74	22	2.21	1.47	<10	0.30	532	66	2.35	5	460	22	<5	<20	450	0.15	<10	21	<10	5	100
106	G082106	0.2	6.47	15	1320	<5	0.61	<1	<1	62	27	0.61	3.20	20	0.04	90	97	1.62	3	150	38	<5	<20	216	0.03	<10	3	<10	9	64

ICP: 4 ACID DIG EST/ICP-FINISH

AG: 4 ACID DIG EST/AA-FINISH

Et #.	Tag #	Ag	Al %	As	Ba	Bi	Ca %	Cd	Co	Cr	Cu	Fe %	K %	La	Mg %	Mn	Mo	Na %	Ni	P	Pb	Sb	Sn	Sr	Ti %	U	V	W	Y	Zn
Standard:																														
STSD3		0.5	5.70	25	1305	<5	2.26	1	17	62	42	4.34	1.34	40	1.32	2610	6	1.15	33	1660	52	<5	<20	261	0.35	<10	111	<10	33	212
STSD3		0.4	5.75	25	1395	<5	2.33	1	17	62	43	4.16	1.32	40	1.30	2558	6	1.19	30	1650	52	<5	<20	254	0.34	<10	118	<10	33	207
STSD3		0.5	5.80	25	1345	<5	2.46	1	17	62	42	4.20	1.39	40	1.31	2556	6	1.14	32	1670	56	<5	<20	262	0.35	<10	120	<10	32	205
STSD3		0.6	5.70	25	1315	<5	2.51	<1	17	62	42	4.21	1.39	40	1.31	2568	7	1.15	32	1680	56	<5	<20	266	0.35	<10	119	<10	32	208

JJ/dc
dl/1264-sub
XLS/07

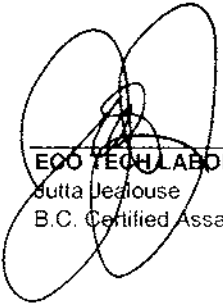

ECO TECH LABORATORY LTD.
Jutta Jegouse
B.C. Certified Assayer