

ASSESSMENT REPORT

of the

2008 EXPLORATION PROGRAM

on the

ZYMO PROPERTY,

OMINECA MINING DISTRICT, BRITISH COLUMBIA

NTS: 93L/13, 103I/16

Latitude 54° 49' N, Longitude 127° 57' W

For;

**Canadian Gold Hunter Corp.
2101-885 W. Georgia St
Vancouver, B.C.
V6C 3E8**

and

**Eastfield Resources Ltd.
110-325 Howe St.
Vancouver, B.C.
V6C 1Z7**

By

**R.J. Johnston, P. Geo.
December 22, 2008**

Mincord Exploration Consultants Ltd.

Table of Contents

	Page No.
Introduction	1
Property Description	3
Location, Access and Physiography	4
Exploration History	4
Regional Geology	6
Property Geology	6
Alteration	8
Structure	10
Mineralization	10
2008 Exploration Programme	11
QAQC	11
Geophysical Survey	11
Grid Work	12
Soil Sampling	12
Prospecting and Mapping	13
Drill Programme	13
Discussion of Exploration Results	16
Geochemistry	16
Geophysics	16
Hobbes Zone	17
FM Zone	20
RD Zone	20
URC Zone	21
Reconnaissance Soil Lines	21
Conclusions and Recommendations	21
Statement of Expenditures	22
Statement of Qualifications	24
References	25

APPENDICES

APPENDIX 1 Drill Logs; ZY08-07 - 12

APPENDIX 2 Analytical Results

LIST OF FIGURES

		Page No.
Figure 1	Location Map	2
Figure 2	Claim Map	5
Figure 3	Regional Geology Map	7
Figure 4	Property Map	9
Figure 5	Property Geology Map	attachment
Figure 6	Cu Geochemistry on Chargeability	attachment
Figure 7	Cu Geochemistry on Airborne Magnetics	attachment
Figure 8	Zymo Cu Geochemistry 2008	attachment
Figure 9	Zymo Au Geochemistry 2008	attachment
Figure 10	Zymo Mo Geochemistry 2008	attachment
Figure 11	Zymo 2008 Chargeability Map	attachment
Figure 12	Zymo 2008 Resistivity Map	attachment
Figure 13	Zymo 2008 Ground Magnetics Map	attachment
Figure 14	Hobbes Zone Drill Hole Locations	attachment
Figure 15	ZY08-07,08 Drill Section	attachment
Figure 16	ZY08-09,10 Drill Section	attachment
Figure 17	ZY08-11 Drill Section	attachment
Figure 18	ZY08-12 Drill Section	attachment

Introduction

The Zymo property is located approximately 45 km west of the town of Smithers in west-central British Columbia. The property is comprised of 27 claims and fractions totaling 10,660.04 hectares. The property is presently under option by Canadian Gold Hunter Corp. from Eastfield Resources Ltd, who in turn has optioned the property from a private Alberta company.

The property is underlain by Hazelton, Bowser and Skeena Group sediments which have been intruded by dioritic rocks of the Cretaceous age Bulkley Suite (?). Most the work to date has been carried out on Zymo Ridge, between Mulwain and Red Canyon Creeks, which is where all of the known mineralization occurs. This ridge is rounded and subdued with a maximum elevation of 1500m, in contrast to the ridges to the northeast and southwest which rise as rugged crags to over 2300m. The Zymo Ridge sediments are intruded by diorites, whereas the intrusive rocks north of Mulwain Creek are leucocratic granites, probably of the younger Eocene Nanika Suite.


Porphyry type copper-gold mineralization was discovered on the property in the mid 1980's during follow-up of regional copper and stream sediment anomalies generated from government surveys. Freeport Copper Company optioned the property in 1999 and drilled six diamond drill holes which encountered anomalous copper and gold values in phyllic altered intrusive rocks in the FM Zone area. NDT Resources took an option over the property in 2004 and flew an airborne geophysical survey, but did not conduct any surface work. Eastfield Resources optioned the property in 2007 and conducted an extensive steam sediment sampling programme, along with soil sampling, mapping and prospecting which included the west side of Zymo ridge which was not previously explored. The Hobbes Zone was discovered in this area, returning values up to 0.33% Cu and 1.1g/t Au from rock samples within a large Cu-Au soil anomaly.

In 2008 Canadian Gold Hunter and Eastfield conducted a programme of soil sampling, ground geophysics, mapping, prospecting and drilling over the property. The IP survey revealed a chargeability anomaly that is up to three km wide and six kilometres long and open ended to the southeast and northwest. Prospecting and mapping revealed the large surface extent of the Hobbes Zone and also discovered a number of porphyry and base/precious metal vein showings on the southwest side of Zymo Ridge, above Red Canyon Creek. Six diamond drill holes, totaling 1554 metres, were drilled in the Hobbes Zone.

Porphyry type copper-gold mineralization on the Zymo property occurs in porphyritic diorites and adjacent sediments in zones of strong quartz-magnetite+/-biotite-k-feldspar alteration. This mineralization is surrounded by extensive zones of phyllic sericite-pyrite alteration, which in turn is hosted with a much larger zone of iron carbonate alteration. Two major areas porphyry mineralization and a number of smaller showings have been discovered so far on the property. The best mineralization to date occurs at the Hobbes Showing, discovered by Eastfield in 2007. The showing area consists of a core of potassic altered diorite porphyry with strong magnetite alteration, disseminated and stockwork chalcopyrite, and mineralized, silicified, chloritic fine grained intrusions/volcanic rocks in Hobbes Creek, which are located at the north side of a 1.5 x 1.5 kilometre area of locally strong copper-gold anomalies in rocks, soils and silt samples known as the Hobbes Zone. Drilling in 2008 here returned intercepts of 72.0m of 0.72% Cu and 0.54g/t Au in hole ZY08-09 and 158.95m of 0.31% Cu and 0.21g/t Au in hole ZY08-10.

The FM Zone (referred to as the Main Zone in the 2007 Eastfield report) is located four kilometres to the east of Hobbes and is a four square kilometre porphyritic diorite intrusion with widespread sericite-pyrite alteration and local structurally controlled zones of silicification. The 1999 drilling here encountered wide intervals of strongly anomalous Cu-Au mineralization, and surface sampling has returned values of up to 0.92% Cu. Auriferous base metal veins are well known from the north and east sides of this area.

Figure 1:

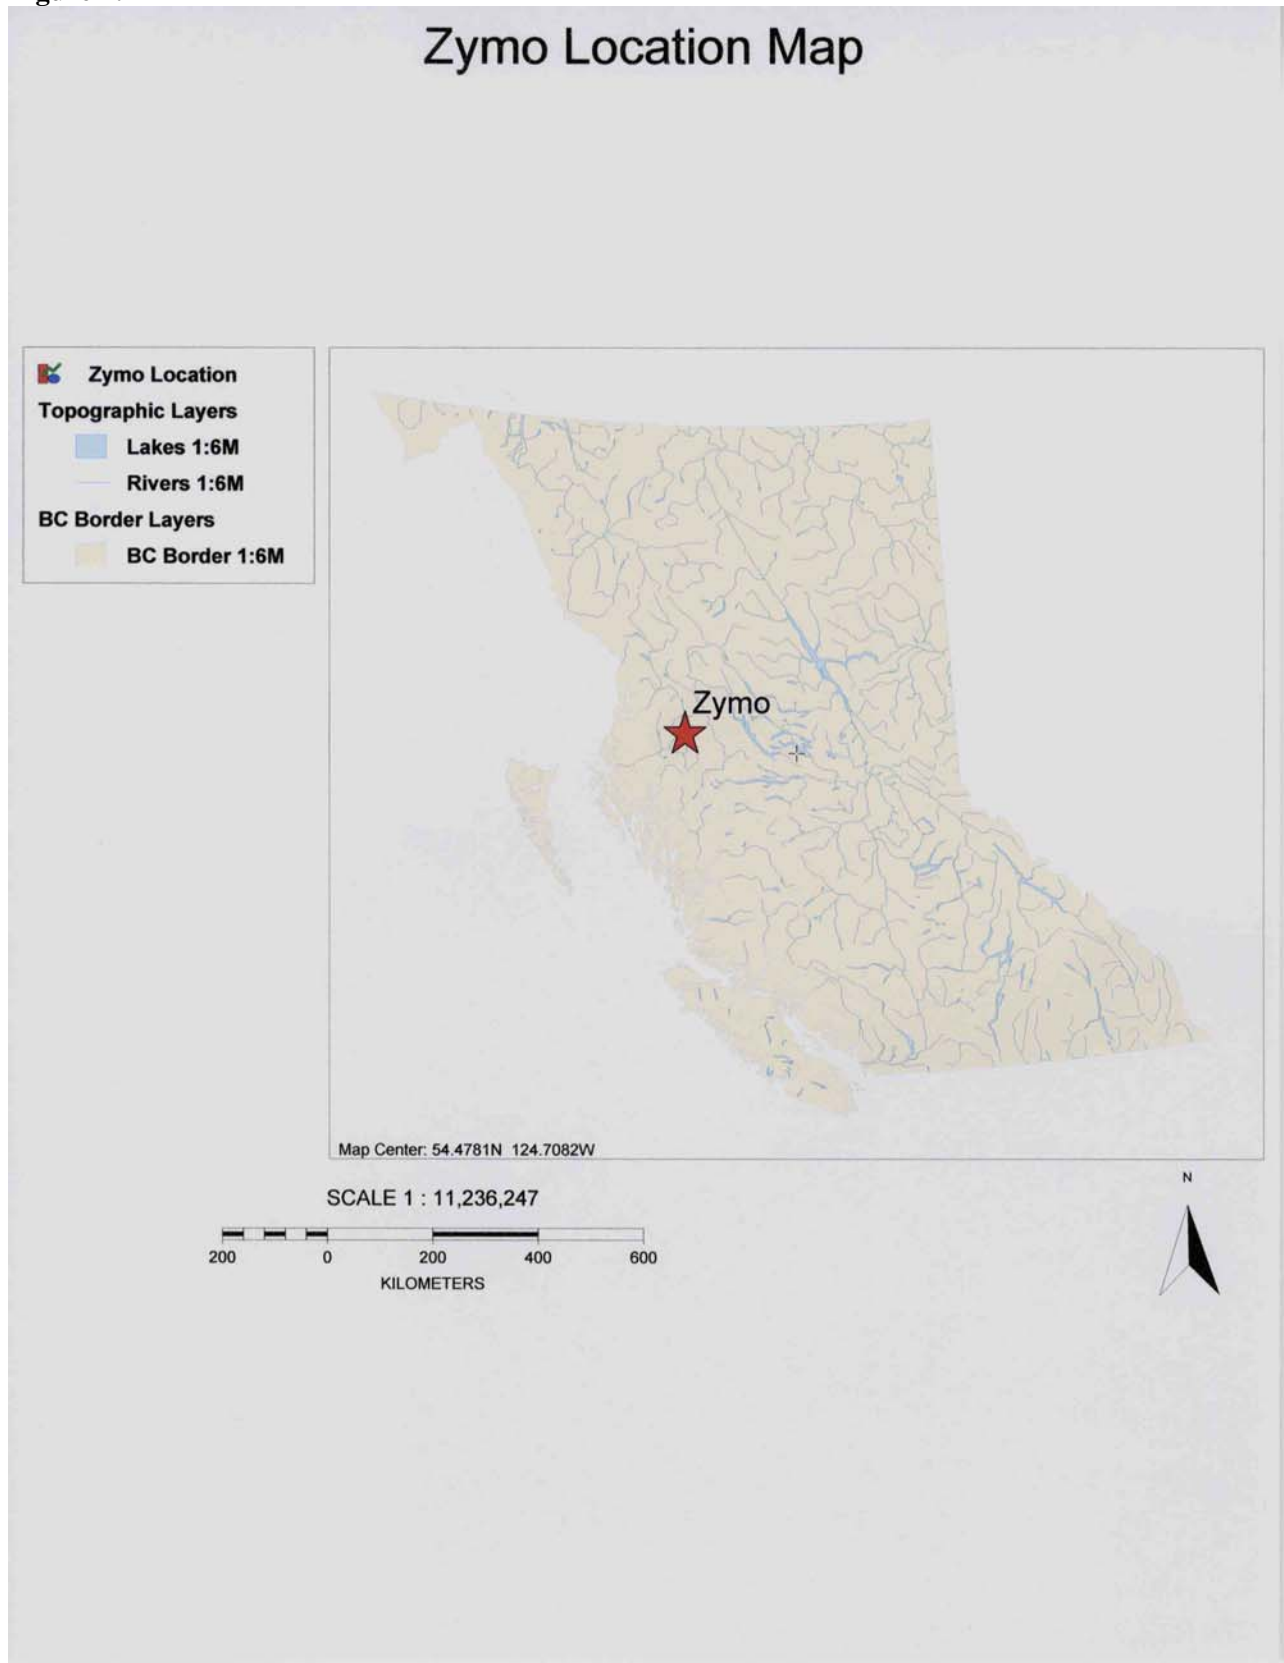

Two new zones of interest were also generated during the 2008 programme, both on the (southwest) Red Canyon Creek side of Zymo ridge. The RD Zone is located two kilometres southwest of the FM intrusive and the URC Zone is located two kilometres west of Hobbes. Both are defined by strong soil and rock geochemistry and lie on the southern edge of the chargeability high and the northern edge of the magnetic high that runs along Red Canyon Creek. The RD Zone also hosts auriferous base metal veins with up to 17.6 g/t Au and 568g/t Ag, and altered intrusive float. In the URC area, mineralized float and outcrop contains values to 0.31% Cu and 0.15g/t Au within a moderate copper-gold soil anomaly.

The next phase of exploration on the property should consist of extending and in-filling the geophysical grid to determine the extent of the chargeability anomaly which defines the area of interest, and to also understand the relationship with alteration and mineralization with resistivity and magnetics. The soil sampling, prospecting and mapping should also be continued, with a view to better understanding the present zones of mineralization, discovering new ones, primarily in the Red Canyon Creek area, and to identifying targets for further drilling.

Property Description

The Zymo property is located in the Omineca Mining Division and is comprised of 27 legacy and cell claims and fractions totaling 10,660.04 hectares. Eastfield Resources Ltd. has the option to earn a 100% interest in the Zymo property from 811537 Alberta Ltd. by making a total of \$250,000 in cash payments, issuing 600,000 shares and completing \$1,000,000 in exploration expenditures over a five year period and reserving a 3% NSR for the vendor. The NSR on copper production may be reduced to 1.5% by paying the vendors \$1,500,000.

In 2008 Eastfield optioned the Zymo property to Canadian Gold Hunter Corp. under an arrangement by which they have the option to earn a 60% interest in the property from Eastfield by completing exploration expenditures of \$4 million and make cash payments of \$300,000 over five years, and issue 50,000 shares. Canadian Gold Hunter may earn an additional 10% interest by completing a feasibility study and an additional 5% by arranging mine financing for Eastfield.

Table 1: Claim data

Claim Name	Record #	Area (hectares)	Expiry Date
ZYMO-7	345732	500	2018/FEB/18
ZYMO-8	345733	500	2018/FEB/18
ZYMO-9	354273	500	2018/FEB/18
ZYMO-10	354274	500	2018/FEB/18
ZYMO-11	367693	500	2018/FEB/18
ZYMO-12	367694	500	2018/FEB/18
ZYMO-13	367695	500	2018/FEB/18
ZYMO-14	367696	500	2008-FEB/18
ZYMO-15	367697	500	2018/FEB/18
ZYMO-16	367698	500	2018/FEB/18
ZYMO-17	367699	500	2018/FEB/18
MULWAIN4	502772	447.019	2018/JAN/13
MULWAIN3	502767	447.291	2018/JAN/13
ZYMO-19	559923	446.9292	2018/June/5
ZYMO-20	559925	447.0642	2018/June/5
	560326	447.499	2018/June/8
ZYMO	560327	465.6212	2018/June/8
	560328	446.7672	2018/June/8
	560329	465.4257	2018/June/8
	560330	446.8810	2018/June/8
	560331	447.6621	2018/June/8
Z east FR	560332	149.0834	2018/June/8
	594778	74.488	2009/Nov/24

	594779	111.761	2009/Nov/24
	584918	18.627	2018/May/22
Zymo N Frac	594510	223.4299	2009/Nov/18
	594778	74.488	2009/Nov/24
Total:	27 claims	10,660.04 hectares	

Location, Access and Physiography

The Zymo property is located approximately 45 km west of the town of Smithers, B.C. Smithers is a regional centre with scheduled daily air service from Vancouver and a wide variety of service and equipment suppliers as well as government agencies offices. The property is accessed by logging haul roads from Smithers that could provide year round access. This road follows along the north side of Mulwain Creek into the centre of the property and where a bridge has been built across the creek giving possible access for future road networks on Zymo Ridge. Driving time from Smithers to the Mulwain Bridge is approximately one hour. Access to Zymo Ridge and other parts of the property is via helicopter.

The property lies in the Hazelton Mountain Range and is centered on a WNW trending ridge which is situated between Mulwain and Red Canyon Creeks. This feature (Zymo Ridge) is of generally subdued topography and elevation, up to 1500m, in sharp contrast to the 2300+ metre high mountains on either side. This ridge is covered with mature forest but is marked by a large number of grassy bogs that offer good helicopter access. These bogs are generally elongated parallel to the ridge and its bounding creeks, suggesting a structural component to their origins. Seven Sisters Provincial Park lies to the northwest of the property.

The property lies in an area of overlapping claims by two First Nations groups, the Gitksan (Kitwanga, BC) and the Kitselas (Terrace, BC). The company is not aware of any known archeological sites on the property (none are shown on the Map Place government maps). Both groups have been updated on the 2008 work programme.

Exploration History

Prior to 2007, all of the recorded surface work in the Zymo Ridge area was carried out on the east half of the current property. The first noted discovery of mineralization in this area was by Corona Corporation in 1987 on the Calvin claim. In following up a government regional geochemical survey gold anomaly on Red Canyon Creek, they noted anomalous gold values in a quartz-sericite-pyrite altered intrusion. Small programs by the optionee in 1990-1 and 1996-7-8 were geochemical sampling programs including stream sediment, rock sampling, and the emplacement of a soil grid. Porphyry type and auriferous base metal vein mineralization was discovered over what is now referred to as the FM Zone. A six hole, 1148 metre drilling program was completed by Freeport Copper Company in 1999 over the FM Zone, which encountered sericite-pyrite and local quartz alteration and long intervals of strongly anomalous copper values. An 823 line-kilometre airborne geophysical survey was completed in December, 2004 by NDT Ventures Ltd, which covered Zymo Ridge from the southeast end to as far as the Hobbes Zone area.

In 2007 Eastfield Resources carried out a reconnaissance exploration program in late September-early October. The program was designed to look at known areas of mineralization to understand the geology, mineralization and alteration, and to assess the economic potential of the rest of the property. All of the Zymo Ridge drainages were sampled, the existing FM area soil grids were extended to the north and west, reconnaissance soil lines were emplaced, and prospecting and reconnaissance mapping were carried out across large parts of Zymo ridge and the road accessible areas north of Mulwain Creek.

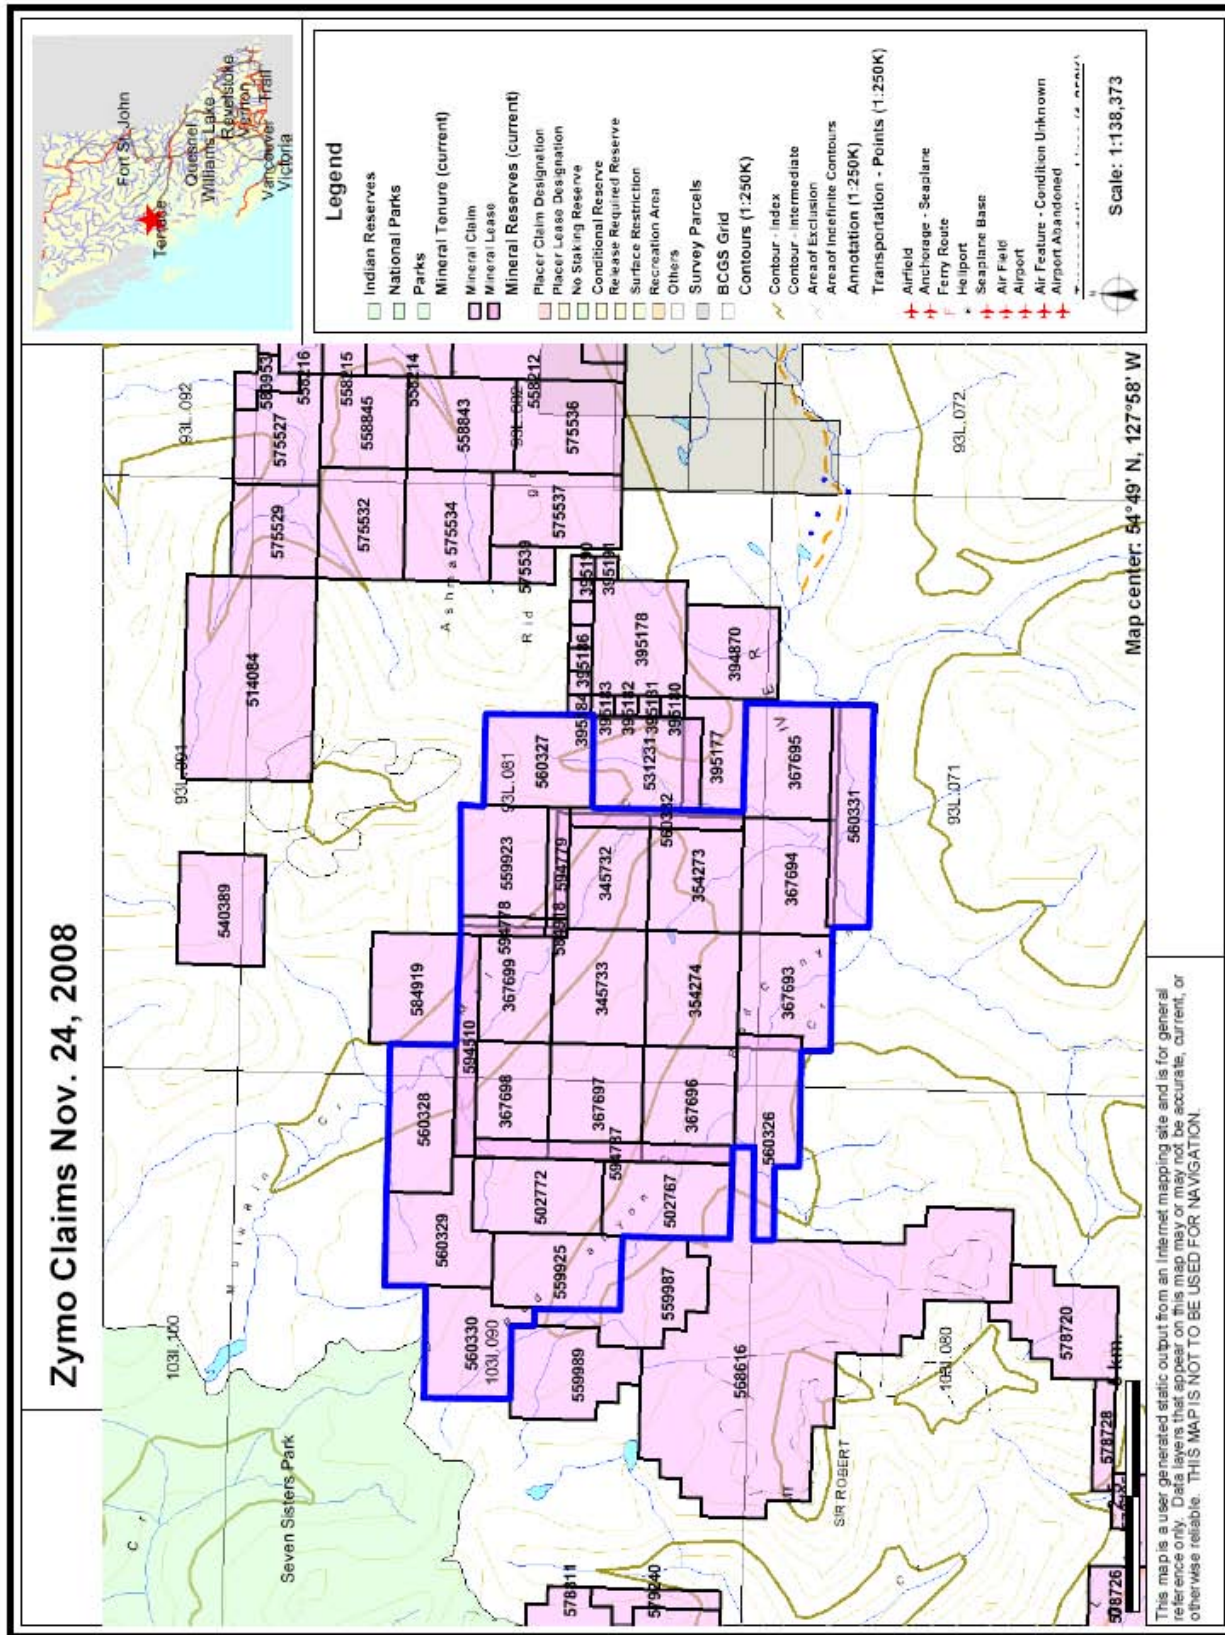


Figure 2: Zymo Property Claim Map

Silt sampling returned a number of Cu-Au anomalies on the Red Canyon Creek (southwest) side of Zymo Ridge, and soil sampling extended the FM Zone Cu-Au anomalies to the north and northwest. Prospecting and mapping encountered new areas of intrusive rocks, often correlating with magnetic highs from the 2004 airborne survey. The FM Zone was mapped and prospected and was found to be a large, strongly phyllic altered intrusive with local silicified zones. One of these, the FM showing was chip sampled and returned 0.11% Cu and 0.23g/t Au over 95 metres. A new showing, the 2Bob, was found midway between the 1999 drill holes ZY-99-01 and 05, returning 0.92% Cu and 0.25 g/t Au from a silicified structure containing chalcopyrite and bornite. Neither of these showings were tested in the Freeport drilling. A new showing, named the Hobbes Zone, was discovered four kilometres west of the 1999 drilling in the follow up of a strong aeromagnetic high. This new showing, of silicified intrusive rocks with disseminated pyrite and chalcopyrite, returned values to 0.33% Cu and 1.1g/t Au, within a strong Cu-Au soil anomaly.

Regional Geology

The Zymo property is located within the Stikine Terrane at the southern edge of the Bowser Basin. The area is largely underlain by clastic sedimentary rocks of the Skeena (early Cretaceous), Bowser (middle-late Jurassic) and Hazelton (early Jurassic) Groups, with Hazelton volcanic rocks mapped in the southeast part of the claims. These rocks have been intruded by granite and diorite of the Eocene Nanika and late Cretaceous Bulkley Intrusive suites. Intrusive rocks on Ashman Ridge, north of Mulwain Creek, are leucocratic granitic rocks (Nanika?), which are markedly different to the diorites found on Zymo Ridge, which may be part of the Bulkley suite. There are differing versions of the geology of the area;

Strong west-northwest to northwesterly trends are reflected in several elements and may describe regional structures. Red Canyon and Mulwain Creeks display parallel northwesterly trends which are also very evident in the airborne magnetic survey in their vicinity. East-west trending surface lineaments can be seen in locations on Zymo Ridge.

Property Geology

Outcrop on Zymo Ridge is quite variable, with very good exposures in local creeks in steep and moderate terrain, with only local rubble and subcrop elsewhere. Strong alteration is widespread and field identifications often difficult. Sample specimens were slabbed in camp which assisted greatly in deciphering lithology and alteration

The geology of the property is composed of various formations of fine to coarse clastic sediments which host numerous intrusions of dioritic rocks. The intrusions are often porphyritic and range from dykes to bodies over four square kilometres in size. Volcanic rocks of the Hazelton Group (Telkwa Formation) have been mapped on the property on the southwest side of Red Canyon Creek, but current work has not yet reached that area.

Mapping to date has defined two distinct units on Zymo ridge; a northern unit defined by abundant weakly altered cobble conglomerate beds, and a southern one that contains finer clastic rocks and widespread alteration, diorite intrusions and all of the known mineralization on the property. The contact is roughly defined by the chargeability anomaly that was discovered in the 2008 geophysical survey, with the anomaly occurring in the southern unit. It runs from Mulwain Creek and the north side of the FM intrusion west-northwest to the north side of the Hobbes Zone. This contact coincides roughly with a fault contact on some government geological maps which juxtaposes Skeena Group sediments on the north with Hazelton Group sediments on the south.

Within the postulated south unit, red and maroon exposures are common in the east and southeast parts of the property, in the Zymoetz River and in Red Canyon Creek. Float containing fragments of large (30cm) ammonites has been found on the southwest side of Zymo ridge in the URC Zone area indicating that these rocks probably belong to the Smithers Formation of the Hazelton Group, which correlates with the mapped volcanic rocks of the Telkwa Formation of the Hazelton Group on the southwest side of Red Canyon Creek.

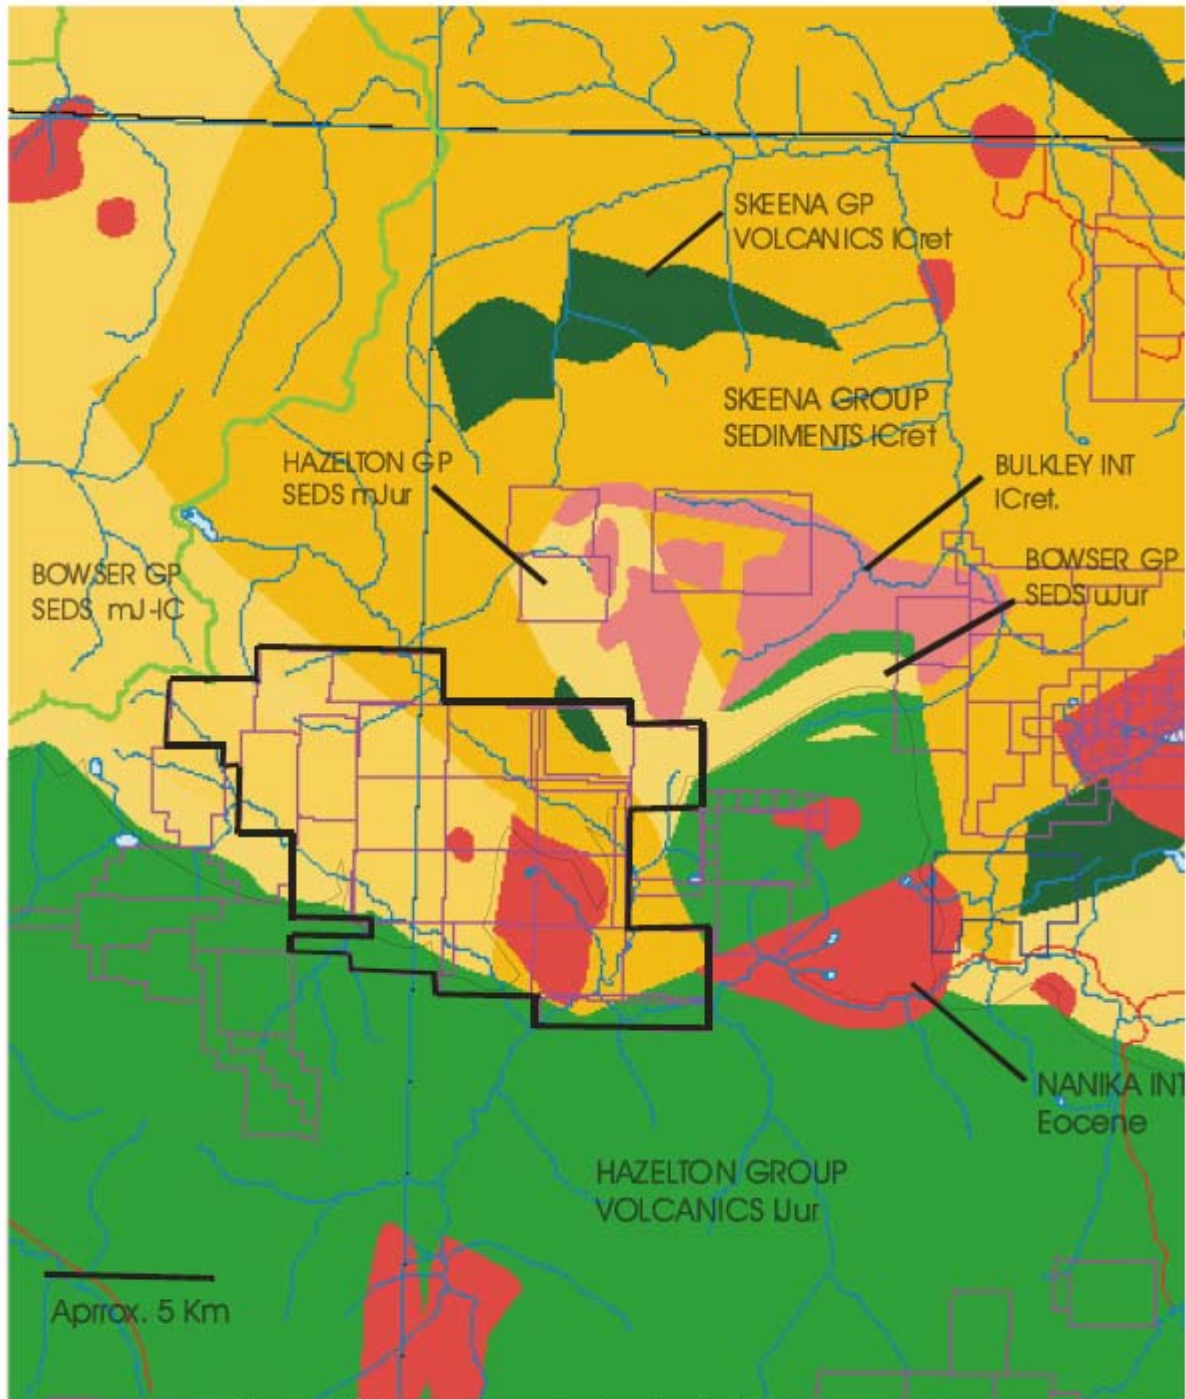


Figure 3: Zymo Property: Regional Geology

Local exposures of intermediate volcanics, red and green tuffs and agglomerates, have been noted within the sedimentary rocks, in both units, probably as intraformational beds, which vary in size to a maximum of about 10 metres in thickness. Basalt was noted in one locality in the Red Canyon Creek area at 564500/607410. Strongly chloritic rocks occur in Hobbes Creek and have been noted in the Hobbes drill core, which are often strongly silicified and can contain significant copper mineralization. A petrographic report from August 2008 described one of these as a volcanic pebble breccia. More samples have been submitted for petrographic analysis, and results are expected in early January 2009.

Dioritic intrusive rocks are common across Zymo Ridge as dykes and bodies up to four km², such as at the FM Zone. The larger bodies are generally porphyritic and often strongly sericite-pyrite altered. Zones of silicification, magnetite and k-feldspar alteration are coincident with chalcopyrite mineralization. The larger diorite bodies show as prominent magnetic highs in both the 2004 airborne and 2008 ground magnetic surveys. In the Hobbes Zone area there are fresh and unaltered diorite bodies close to the mineralized intrusions and post-mineral feldspar porphyry dykes were noted in the drill core from the Hobbes Zone. Local intrusive breccias have been found across Zymo Ridge, and contain copper values comparable to the surrounding intrusive rocks.

Alteration

The alteration pattern around the copper mineralization on the Zymo property fits well into the porphyry copper model and can be described as being centred by a potassic (silica-k-feldspar-magnetite) core, surrounded by a sericite-pyrite phyllic zone which is contained within a much larger halo of iron carbonate alteration. The auriferous base metal veins in the phyllic altered zone also fit this pattern. The alteration patterns are readily visible in geophysics. The sericite-pyrite alteration creates a widespread chargeability high and the magnetite and silicification of the mineralized zones shows as magnetic and resistivity highs within these.

The strongest potassic alteration at the Hobbes Zone coincides with the best mineralization and is readily evident in the 2008 drill core. Porphyritic diorite rocks have been intensely silicified and cut by two to three directions of light grey-white quartz veins up to one centimetre in width. The most prominent direction is roughly east-west, dipping moderately to the south. Magnetite also occurs as flooding and discrete veins. Pink k-feldspar alteration haloes occur around local fractures. This, combined with the local alteration of magnetite to hematite, give sections of the core a pink colour. The zone of strong mineralization is also host to green sausserite alteration, which may be a later event as magnetite is relatively rare where this is seen, though quartz and mineralization are similar to the surrounding rocks.

Around the larger intrusions at Hobbes, the surrounding sediments and smaller dykes are strongly hornfelsed to biotite and chlorite, while sericite and pyrite alteration forms a larger halo around these. Strong chlorite alteration occurs in locally silicified and mineralized volcanic/fine grained intrusive(?) outcrop in Hobbes Creek.

The FM Zone intrusion is extensively and strongly sericite-pyrite altered, with pyrite contents to over 5%. Quartz veins are common locally, and pervasive silicification occurs in local structures usually with chalcopyrite and sometimes bornite such as the 2Bob Showing. Copper values in the sericite-pyrite zones are generally anomalous, and may reach 0.1% in areas of very high pyrite content.

Biotite alteration has been noted around the 2Bob showing and as biotite in sericite altered sediments two kilometres farther east. At Hobbes, strong biotite alteration is very common in sediments and dykes on the periphery of the quartz-magnetite-k-feldspar altered mineralized diorite porphyry, and as widespread hornfels alteration of the host sediments and volcanics.

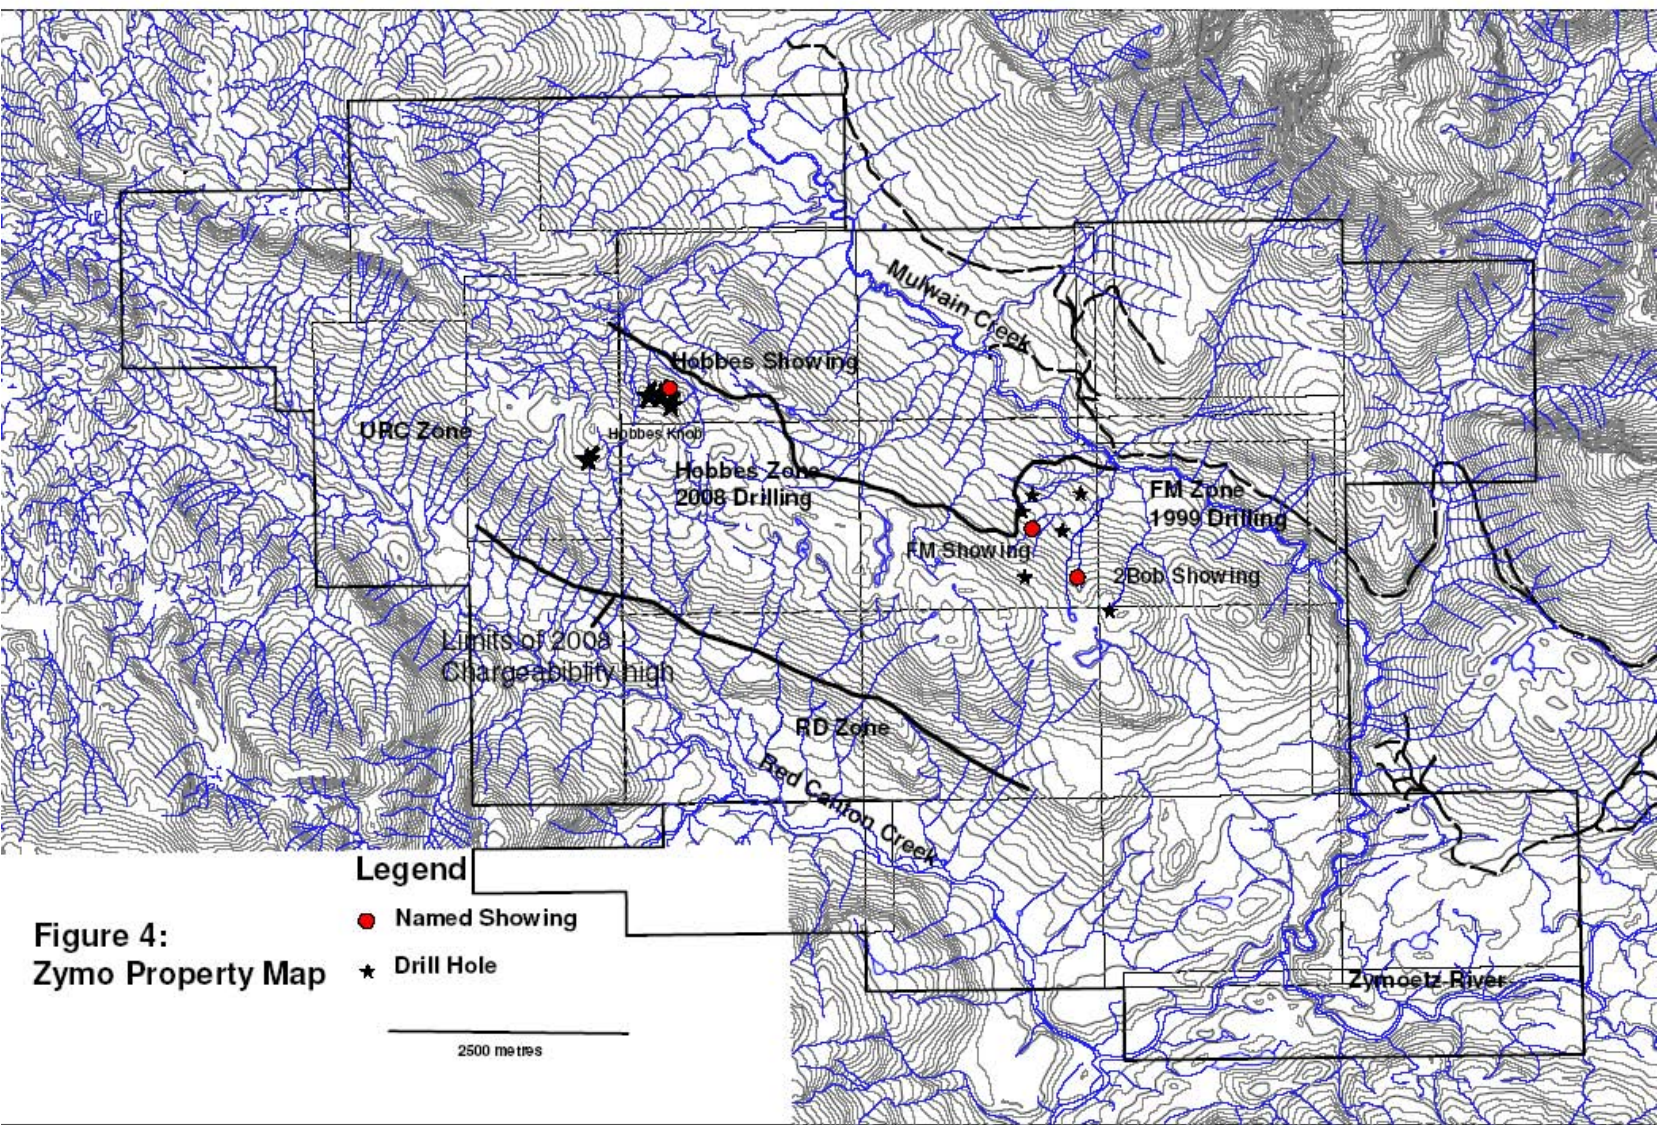


Figure 4:
Zymo Property Map

Structure

A strong west-northwest fabric is obvious on the property, manifesting itself as topographical and geophysical features and dyke orientations. This direction is parallel to the regional structural grain of this part of British Columbia. The best mineralization at the FM Showing is near a NNE trending probable fault contact with carbonate altered sediments. At the 2Bob Showing, located 650 metres southeast, bornite and chalcopyrite occur in a 0.75 metre wide silicified structure that runs az150°/vertical. Grab samples from here ran up to 0.92% Cu and 0.26g/t Au.

In the Hobbes area, petrographic work has identified mylonite in Hobbes Creek, west of the Hobbes Showing, and similar rocks were noted in the 2008 drill holes here. Brecciated volcanic rocks were also found in the area, but due to the strong alteration it is often difficult to tell if these are tectonic. In upper Hobbes Creek, 230 metres southwest of ZY08-07, there is a five metre wide az 150° fracture/shear that is very strongly altered with iron carbonate. Similar smaller east-west trending altered fracture zones occur north on the creek. These fracture zones are well mineralized and locally contain chalcopyrite veins to one centimetre. At 196 metres in hole ZY08-10, a five metres broken fracture zone marks a sharp change in mineralization, from 0.29% Cu above to 0.03% Cu below, though with no major change in lithology or alteration.

Government maps indicate that the Hobbes Zone is located on a north-northwest trending fault contact between Skeena Group sediments on the north-northeast and Hazelton Group sediments on the south-southwest side.

Mineralization

The main style of mineralization on the Zymo property is calc-alkaline copper-gold porphyry type, best exposed in the Hobbes Showing, which is located at the north end of the Hobbes Zone, a 1.5 x1.5 kilometre area with locally strong copper-gold-molybdenum geochemistry in rock, soils and silt samples. In the Hobbes Showing chalcopyrite occurs as stockworks, veins and disseminations in strongly silicified magnetite-k-feldspar altered porphyritic diorites and adjacent sediments, surrounded by a halo of sericite-pyrite alteration which contains variably anomalous copper values in rocks and soils. Surface samples have returned values to 0.86% Cu and 0.65g/t Au. Some of the 2008 drill results from here include 72.0 metres of 0.72% Cu and 0.54g/t Au in ZY08-09, and 158.95 metres of 0.31% Cu and 0.21g/t Au in ZY08-10. Gold correlates very well with copper values at Hobbes at a ratio of 1% Cu=0.8g/t Au. Molybdenum occurs to levels of 0.009% over 38 metres on the edge of the highest Cu-Au zones.

Chalcopyrite is the only copper sulphide noted on the property save for a single exposure containing bornite in a silicified structure in the eastern part of the FM Zone, referred to as the 2Bob showing. Polished section work found minor bornite and chalcocite with chalcopyrite in another sample from the FM Zone.

Even in areas containing abundant chalcopyrite malachite is rare, possibly due to the acidic nature of the groundwater as a result of the weathering of the abundant pyrite in the extensive phyllic altered zones. Localized occurrences of molybdenite are common in the Hobbes area, noted both in outcrop and in drill core.

Auriferous base metal sulfide veins have been noted in a number of locations on the eastern side of the property. The veins are as large as 1m in width and can be traced for over 100m. The veins have no consistent orientation and are composed dominantly of pyrite, with lesser amounts of sphalerite, galena and chalcopyrite. These veins commonly contain over 1 g/t Au, to a high of 17.6 g/t Au along with 568 g/t Ag.

These veins are well known in the FM Zone area from the earliest days of prospecting there, occurring peripherally to, and on the edges of the intrusive. In 2007 and 2008 more veins were found on the Red Canyon Creek side of Zymo ridge in an area referred to as the RD Zone. This area also hosts variable sericite-pyrite altered sediments and dykes and is coincident with a large airborne magnetic anomaly. None of these veins have yet been found in the Hobbes area.

2008 Work Programme

The 2008 exploration program on the Zymo Property was carried out by Mincord Exploration Consultants Ltd. of Vancouver BC., from late June to early October. The work was conducted out of the Copper River Ranch, a lodge located on McDonnell Lake, 20km southeast of the Zymo property, and connected by road to the town of Smithers and to the logging roads that access the north part of the Zymo Property. Access to Zymo Ridge was by Interior Helicopters' Bell Jet Ranger that was based in Smithers.

The work programme was composed of an IP and ground magnetics survey, soil and silt sampling, mapping and prospecting, followed up by a six hole, 1554.47 metre, diamond drill program in September. A total of 1193 soils, 51 silt, and 480 rock samples were collected.

QA/QC

A comprehensive system of QA/QC was conducted as an important part of the program to ensure the integrity of the results collected. This involved rigorous sample collection and handling procedures. The rock samples were sealed with a cable lock in the field and stored under the geologist's supervision at the camp at McDonnell Lake. These samples were packed into numbered, sealed rice sacks for delivery to Acme Analytical Laboratories' sample preparation lab located in Smithers. The soil and silt samples were dried in a secure location, also in camp, then delivered to Acme in Smithers.

The drill core was moved daily from the drill sites to camp, where it was logged and split. As with the rock samples, the drill core samples were sealed with cable lock then placed into numbered rice sacks for shipment to the Acme sample preparation lab in Smithers. A prepared standard sample; CDN-CGS-6 from CDN Laboratories, (values of 0.318% Cu and 0.26g/t Au) was inserted into the sample stream at a rate of one per thirty samples.

The samples were ground and split in Smithers by Acme and then moved to their facility in Vancouver for analysis by ICP-Mass Spectrometry for 36 elements using package 1DX15. Acme ran duplicate samples and inserted their own standards in order to maintain their own in-house QAQC programme.

Geophysical Survey - 2008

A total of 44 km of IP survey and 43.7 km of magnetometer survey were performed at the Zymo Property by Scott Geophysics Ltd. of Vancouver from August 12 to September 9, 2008. The pole-dipole array used for the IP survey was an "a" spacing of 50 metres and "n" separations of 1 to 4 plus at an "a" spacing of 100m and "n" separations of 3 and 4 (50/1-4 & 100/3-4). The on line current electrode was located to the south of the potential electrodes on lines 8800W to 10800W and to the north of the current electrode for the south extension of line 10200W and lines 12000W to 14600W. The survey was conducted along lines that were compassed, tight chained and cut during 2008. All stations and end point locations were captured by GPS. The 150 metre data gap on L98W is due to a treacherous canyon which was unsafe to run grid lines across.

The survey was divided roughly equally over the Hobbes and FM areas, with a southwest extension made from each of these grids to cover a large airborne magnetic anomaly near Red Canyon Creek. Line spacing was generally 200 metres, though the end lines on the FM grid were 400 metres apart. A single line was emplaced between the two grids and showed well the continuity of the chargeability high across Zymo ridge.

The IP survey revealed a chargeability high that runs along Zymo Ridge for over six kilometres, and is 2.0 to 3.0 km in width. Both the Hobbes and FM zones are located on the north side of the chargeability high. The Hobbes and FM zones are located on the north side of the chargeability high, while the RD and URC Zones are located around the southern edge.

The plot of resistivity shows a moderate high that roughly corresponds with the chargeability anomaly, though with stronger highs occurring within this. The Hobbes Showing is marked by a small strong resistivity high over the strongly silicified intrusives there. A number of other strong highs occur to the southwest of this, some up to 300 metre wide. Two small strong resistivity highs are noted from the FM Zone; one within the sericite-pyrite altered FM intrusive and another in sediments outside of the chargeability high

A ground magnetic survey was carried out in conjunction with the IP programme. Readings were taken at 25 metres stations along the lines, though tightened up to 12.5 metres in area of high magnetic gradient. Readings were corrected with a base station that was set up at camp. Overall the results show little obvious correlation with geology or other geophysical signatures, but correlate well with the airborne survey of 2004. The Hobbes Zone, with its strong magnetite alteration, showed up well as a large strong anomaly, and a number of other small magnetic highs are present in both the FM and Hobbes areas. The two southwest extension lines verified the Red Canyon Creek magnetic high discovered in the airborne survey.

Grid Work - 2008

A grid was emplaced over a large part of Zymo ridge in 2008, covering the Hobbes and FM Zones, and in two areas on the southwest side of the ridge, above Red Canyon Creek. The lines were oriented at azimuth 030°, roughly perpendicular to the general geologic grain, and generally at 200m wide spacing. The lines over the Hobbes and FM Zones were cut to enable the geophysical program proceed along them. Fifty metre stations were tight-chained and marked with wooden pickets numbered with the station coordinates, while the 25 metre stations were flagged. No baseline was emplaced; the starting point for the lines was located by GPS, and the lines compassed from there.

The lines are given west numbering with north stations along the lines. The FM grid extends from L88W to 104W, from near the top of the ridge at about 100+00N, northeast to near Mulwain Creek at approximately 123+00N. L102W was extended southwest to Red Canyon Creek in order to place a geophysical line over a magnetic high there. This cut grid covers the northern part of the 1990's and 2007 soil sample grids, which were oriented somewhat east-west.

The Hobbes grid ran from L130W to 144W, from the southwest side of Zymo ridge for about two kilometres to the northeast, from approximately 90+00N to 110+00N. This grid was located over the top of Zymo Ridge, roughly centered on a prominent topographic high referred to as Hobbes Knob. One line, L140W, was also extended to the southeast to Red Canyon Creek. Lines 116 and 120W were emplaced between the two grids in order to test the continuity of the chargeability anomalies discovered in the two grids, though due to time constraints, only L120W was run.

Two soil sampling grids were emplaced over targets on the southwest side of Zymo Ridge, in the Red Canyon Creek area. These lines were compassed and flagged only. The RD Grid is located one kilometre southeast of the FM Zone, and covers a strong aeromagnetic high which contains a number of auriferous base metal veins, local dykes and local sericite-pyrite altered sediments. This grid ran from L94W to L112W. Lines 98, 100 and 102W ran from the FM grid southwest to Red Canyon Creek, while the rest started at 93+00N.

The URC grid was located 1.5 kilometres west of the Hobbes grid, and 4.6 kilometres northwest of the RD grid. It consists of four lines; L158 to 162W, which covered part of an area where altered mineralized intrusive float was discovered in 2008.

Soil Sampling - 2008

A total of 1193 soil samples were collected during the 2008 programme; along most of the cut lines and all of the flagged grid lines and on a number reconnaissance lines over outlying targets. Samples were collected at 50 metre intervals. Sample locations were captured on GPS, and sample data recorded for each station. A number of stations were not sampled due to the large number of bogs and swamps on Zymo Ridge and all samples were run for 36 element ICP.

The FM grid covers the northern part of the 1990's and 2007 soil sampling grid. Lines 88-92W were sampled in their entirety as a check of previous results, especially in the area of the two main showings there; the FM and 2Bob and the other lines were sampled north of the earlier work. All of the Hobbes grid was sampled, though lines 116 and 120W, located between the two main grids, were not soil sampled.

Two other grids, the RD and URC, described above, were sampled as well. The southeast parts of the RD grid lines, up to 500 metres in length, are situated on the wide flood plain of Red Canyon Creek, underlain entirely by river gravels so samples were not collected here.

A number of reconnaissance soil lines were emplaced around the property to cover other targets. These lines were not compassed and only the sample stations are flagged. Two such lines covered airborne magnetic highs in the very southeast part of the property, two were emplaced as follow up to a weak copper in silt anomaly on the north side of Mulwain Creek, and two others were installed over the southwest side of Zymo Ridge between the RD and URC grids.

Prospecting and Mapping - 2008

The FM, and especially the Hobbes Zone, were mapped and sampled during 2008 in order to understand the geology and alteration. This work in the Hobbes Zone revealed the large surface extent of the quartz-magnetite altered mineralized diorite porphyry bodies there, with outlying mineralization in silicified chloritic possible volcanic rocks. Strong quartz stockworks with magnetite and chalcopyrite veining were found over an area of 350 by 100 metres, with values as high as 0.86% Cu and 0.69g/t Au, with 0.1% Cu common in the outlying rocks.

Prospecting was conducted along the Red Canyon Creek side of Zymo Ridge to follow up on copper and gold stream sediment anomalies from the 2007 programme. From this work came the discovery of the auriferous base metal veins, sericite-pyrite alteration and dykes in the RD Zone. The largest vein found to date, the RD Showing, is up to one metre wide and over 100 metres long and carries gold and silver grades of 17.6 and 568g/t, respectively. Prospecting also discovered silicified altered mineralized float and outcrop from the URC Zone, west of Hobbes where samples returned values of up to 0.33% Cu and 0.22g/t Au in float, and 0.15% Cu and 0.09g/t Au in outcrop.

A total of 480 rock samples were collected through the season along with 51 silt samples. Large parts of Zymo Ridge as well as the area southwest of Red Canyon Creek still need mapping and prospecting work

Drill Programme - 2008

Six NQ diamond drill holes were drilled in the Hobbes Zone area of the property from Sept 4-19, 2008, totaling 1554.47 metres. The first five of these; ZY08-07 to 11, were drilled into the Hobbes Showing area, and hole ZY08-12 was drilled 1000 m southwest on the south side of Hobbes Knob into a magnetic-resistivity high from the 2008 geophysical survey, in an area containing mineralized intrusive rocks. Overburden was minimal in all of the holes.

The holes were oriented parallel to the 2008 grid lines and inclined to -59 degrees and were located in a manner so as to minimize tree cutting. Sumps were dug to capture the water outflow from the holes. Platforms were built for all of the holes; the first two of these were dismantled and the wood stored on the ZY08-11 platform, and the platform at ZY08-12 was left intact for the time being.

The drilling was conducted by Driftwood Diamond Drilling of Smithers. Drill moves and shift changes were done by helicopter, and the core was flown out daily to the Mulwain Creek bridge area from where it was trucked to camp at McDonnell Lake where it was logged and split, generally on three metre intervals. These samples were sent to Acme Laboratories' sample preparation lab in Smithers and the remaining core was stored at McDonnell Lake.

Table 2: 2008 Drill Data

Zymo 2008 drill data			UTMs in NAD 83 Zone 9							
hole	UTM easting	UTM northing	Grid east	Grid north	Elev (m)	Azimuth	Dip	Depth (m)	Start	Finish
ZY-08-07	562810	6077713	137+75	105+78	1275	30	-59	252.98	4-Sep-08	5-Sep-08
ZY-08-08	562809	6077709	137+75	105+74	1275	210	-59	237.74	6-Sep-08	8-Sep-08
ZY-08-09	562942	6077732	136+70	106+55	1282	27	-59	256.03	8-Sep-08	11-Sep-08
ZY-08-10	562941	6077728	136+70	106+51	1282	208	-59	266.7	11-Sep-08	13-Sep-08
ZY-08-11	563043	6077610	135+22	105+95	1290	37	-59	259.08	14-Sep-08	16-Sep-08
ZY-08-12	562172	6077037	140+00	96+60	1318	40	-59	281.94	17-Sep-08	19-Sep-08
							Total	1554.47		

Hole **ZY08-07** was the first hole of the campaign and targeted an impressive outcrop of intense quartz stockwork with abundant magnetite and chalcopyrite from which bedrock sampling returned 0.42% Cu and 0.7g/t Au. This outcrop is located at the west end of the main body of altered and mineralized diorite porphyry of the Hobbes Showing, which extends for 300 metres east from here. The silicified chloritic mineralized outcrops in Hobbes Creek are 125 metres west.

The hole was located at the north end of a very prominent magnetic high on line 138W, 25 metres west, in an area of moderate to strong (20-40mV) chargeability, and moderate (200-500 ohms) resistivity, based on data from the L138W pseudosections. The drill hole was oriented azimuth 030°, with a dip of -59°, and was 252.98m deep.

The top 201.22 metres intersected diorite porphyry that was variably altered with quartz-magnetite or sausserite. Both the quartz and magnetite alteration consists of pervasive flooding and veining. The green sausserite alteration may be a later overprint, as it appears to remove the magnetite, but does not affect the silica and chalcopyrite. Chalcopyrite occurs as fine disseminations in the flooded zones and in the quartz and magnetite veins and stringers. Pyrite is less common. Local pink sections of core are attributed to hematite alteration of magnetite, and/or pink k-feldspar alteration haloes around fractures. This intrusive interval returned 0.21% Cu and 0.15g/t Au, which included higher grade intervals such as 0.33% Cu and 0.20g/t Au from 119.0 to 182.0m.

The bottom part of the hole intersected siltstone that has been variably biotite-chlorite altered, along with a six metre sausserite altered diorite porphyry dyke, and a three metre interval of a volcanic(?) fragmental unit. The stronger altered siltstones are referred to as hornfels. The biotite and chlorite occurs as fine disseminations and flooding, with silicification and magnetite clots also occurring locally. Chalcopyrite and pyrite occur as disseminations throughout, though chalcopyrite decreases and pyrite increases from the intrusive above. This interval below the main diorite porphyry returned values of 0.14% Cu and 0.094g/t Au. Molybdenum values are much higher in the sediments than the intrusive, increasing from 0.001% to 0.007%. Arsenic values are quite variable, with the highest values occurring in the intrusive, though not necessarily with best copper and gold.

Hole **ZY08-08** was drilled from the same location, but turned 180 degrees to an azimuth of 210 degrees, also at -59°, to a depth of 237.74m. The chargeability and resistivity were about the same as hole ZY08-07, but this hole was drilled from the northern edge into the 150 metre wide magnetic high.

In this hole, the mineralized and altered diorite porphyry body extended to 69.5 metres, with three further dykes to 110.3 metres, which intrude grey siltstone. Below this to the bottom of the hole, the lithologies encountered were siltstone, hornfels, chloritic volcanics and sericite altered fine grained diorite dykes. Chalcopyrite mineralization extended through the diorite porphyry and dyke intervals.

The diorite porphyry interval to 69.0 metres ran 0.20% Cu, 0.13g/t Au, and 0.001% Mo. The dyke-bearing interval from 69.0 to 111.0 metres returned 0.40% Cu, 0.25g/t Au and 0.0014% Mo, while the bottom part of the hole below the diorite porphyry dykes returned 0.12% Cu, 0.073g/t Au and 0.0037% Mo. The best mineralized interval of the hole was in the diorite porphyry dyke section and the lower part of the main diorite porphyry from 51.0-111.0 metres; 60.0m @ 0.39% Cu and 0.26g/t Au. As in ZY08-07, the best molybdenum values are from outside of the diorite porphyry.

Hole **ZY08-09** was collared 140 metres east of holes ZY08-07 and 08, drilled to the north at azimuth 027°, -59°, targeting the middle part of the Hobbes surface showing area which contains mineralized quartz-magnetite altered diorite porphyry outcrops grading up to 0.86% Cu and 0.65g/t Au. The hole is located 70 metres grid west of line 136W. As with ZY08-07, the hole was situated at the north end of a very strong magnetic high, a strong resistivity high (+700 ohms) and in an area of moderate chargeability.

This hole had similar geology as ZY08-07 and returned the best values of the 2008 drilling programme. It was 256.03 metres deep with the top 141.2 metres in the mineralized and altered diorite porphyry. An interval of similar diorite porphyry dykes in siltstone and hornfels extends to 173.75 metres, with the bottom of the hole again in siltstone and hornfels with fine grained diorite dykes. The main diorite porphyry body returned 0.49% Cu and 0.36g/t Au, the diorite

porphyry dyke interval ran 0.17% Cu and 0.09% Au, and the country rock to the bottom of the hole ran 0.11% Cu and 0.07g/t Au.

The entire 252.97 metre length of the hole ran 0.32% Cu and 0.23g/t Au. The 72.0 metre interval from 15.0-87.0m ran 0.72% Cu and 0.54g/t Au, all within the main diorite porphyry body. Chalcopyrite occurs as abundant fine disseminations in the altered diorite porphyry and adjacent altered sediments, in quartz veins and stringers up to one centimetre. The highest values from the hole were from 45.0 to 66.0 metres, which ran 1.01% Cu and 0.76g/t Au, has only local magnetite and no pink k-feldspar alteration.

Hole **ZY08-10** was drilled from the same site as ZY08-09, oriented to the southwest; AZ 208°, -59°, to test the area south of the Hobbes Showings where there is no outcrop. The hole went to 266.70 metres and encountered the altered diorite porphyry dykes in sericite altered country rock to 224 metres, with sericite +/- biotite altered country rock and local fine grained diorite dykes to the end of the hole. As with the previous holes the diorite porphyry was altered to both quartz-magnetite and sausserite. A breccia zone from 195.95-199.17m appears to represent a fault, as copper and gold values both drop markedly below this, though there was no obvious change in lithologies or alteration. The 196 metres above the structure returned 0.29% Cu and 0.19g/t Au, while the bottom of the hole below ran 0.03% Cu and 0.02g/t Au over 68 metres. The best interval of the hole was from 18.0 to 75.0 metres; 57.0m of 0.43% Cu and 0.32g/t Au.

A 10 metre post-mineral feldspar porphyry dyke was encountered at 98 metres. It contains 30% scattered feldspars up to one centimetre in length, with weak sericite alteration. Copper values in this interval averaged 59ppm.

Hole **ZY08-11** was located 160 metres southeast of holes ZY08-09 and 10, targeting the east end of the Hobbes Showings, 78 metres east of L136W. The hole was drilled to 259.08 metres, oriented to the northeast at AZ 037° and inclined to -59°. The hole, for topographic and practical reasons was collared farther back from the diorite porphyry outcrops, and was drilled behind the L136W resistivity high, but across the main part of the magnetic high.

The hole intersected hornfelsed biotite-sericite +/- chlorite altered fine clastic sediments and chlorite altered volcanics(?). These country rocks were cut by numerous diorite porphyry, and lesser diorite dykes. The diorite porphyry dykes lacked the strong quartz-magnetite alteration of the previous holes, and were instead strongly biotite altered. A single feldspar porphyry dyke was also noted. Disseminated and stockwork chalcopyrite occurs throughout the hole, but at lower levels than in previous holes, and pyrite content is higher.

The entire length of the hole returned values of 0.11% Cu and 0.07g/t Au, with the interval from the top of bedrock to 153.0m returning 0.16% Cu and 0.1g/t Au. Molybdenum values were highest with the better Cu values, to 0.006% from 51.0 to 120.0 metres.

The final hole of the 2008 programme, **ZY08-12**, was located one kilometre southwest of the other holes, on the Red Canyon Creek side of Zymo Ridge. This hole was designed to test a new area after the success of the other holes in the Hobbes Showings area. It was collared on L140W and targeted a strong magnetic-resistivity high in an area where mineralized chlorite-magnetite altered intrusive rubble had been discovered. The hole was positioned on the southern edge of the strongest part of the chargeability high that straddles the ridge here. The earlier drill holes were located in a similar location on the north side.

The hole was drilled to a depth of 281.94 metres, to the northeast at AZ 037°, -59° and was composed of biotite-sericite-epidote altered hornfelsed sediments with local strongly biotite altered diorite dykes. Pyrite, in stringers and disseminations was common throughout, to 2%, with chalcopyrite occurring as disseminations, though of lesser amounts. The entire hole ran 0.065% Cu and 0.035g/t Au, while the interval from 51.0 to 150.0 metres returned 0.11% Cu and 0.05g/t Au. Molybdenum values were low, with the best interval was from 135.0 to 180.0m, which returned 0.002% Mo.

Discussion of Exploration Results

Geochemistry Discussion

Geochemical sampling on the Zymo property was undertaken in several passes and is summarized in the following table:

Table 3: Summary of Geochemical Sampling, Zymo Property

Sampler	Year	Rock	Soil	Silt
Corona Corporation	1987-8	69	60	3
Skeena Resources	1990-1	20		77
Robin Day	1996	74		11
Robin Day	1997	50	126	37
Robin Day	1998	42	148	39
Eastfield Resources	2007	136	264	140
Canadian Gold Hunter/Eastfield	2008	480	1193	51
	Total	871	1791	358

To date, some 3020 soil, rock and silt samples have been collected over the Zymo Property, which has given good, but by no means complete coverage of most of Zymo Ridge. Sampling to date indicates that geochemical sampling works well in finding surface mineralization.

Zymo ridge is unusually wet, with abundant swamps and bogs. This high groundwater flow, combined with possible high acidity due to the weathering of the abundant pyrite in the phyllic altered zones increases mobility of metals in the surface environment and raises the possibility of displaced soil anomalies.

The four principal zones on the property; Hobbes, FM, RD and URC, all show up as multi-element geochemical anomalies, though with differing signatures. **Copper** and **gold** are strongly anomalous at Hobbes and FM, but also shows as weaker but widespread anomalies at RD and URC. **Arsenic** and **zinc** display widespread anomalies in all of the zones, but is strongest in the eastern FM and RD areas. **Lead** and **antimony** show as strong anomalies in the FM and RD areas, again associated with the base metal veins, and as a weak anomaly at Hobbes. **Silver** and **gallium** are moderately anomalous at FM, RD and Hobbes. **Molybdenum** is very strong at Hobbes, with weaker anomalies at FM and URC.

In 2008, the copper-gold soil anomaly over the FM zone was extended to the north for up to one kilometre, out of the altered FM intrusion and into the sediments. No mapping or prospecting has yet been carried out in this area. Gold and copper also show up as a weak anomaly southwest of Hobbes, mid way between the RD and URC Zones. These areas have a high priority in the next exploration program.

Geophysics Discussion

An airborne magnetic-resistivity-EM survey was flown over part of Zymo Ridge in 2004, and a ground magnetometer-IP survey was carried over the Hobbes and FM Zones in August and September 2008.

The 2008 IP survey revealed a chargeability high that runs along Zymo Ridge for over six kilometres, open at each end. The zone is about 1.5 kilometres in width, though it increases to three kilometres over the FM intrusive which forms a large bulge on the north side of the anomaly. The north edge of the anomaly shows a sharp gradient; from 5-30mV over 200-400 metres. In the FM area the chargeability rises to over 40 mV in some areas, while at Hobbes a large area of greater than 100mV is located under the topographical high there, which known as Hobbes Knob. The Hobbes Showing lies on the north side of the highest chargeability in a 30mV embayment in the higher values. Hole ZY08-12 targeted mineralized intrusive float on the south side of the 100mV zone.

The two southwest extension lines both extended the main anomaly into the Red Canyon Creek area. In the RD showing area, this anomaly coincides with anomalous Cu in soil geochemistry. The other line on Zymo Ridge, between the two grids showed well the continuity and size of the Zymo chargeability anomaly,

The plot of resistivity shows a moderate high that roughly corresponds with the chargeability anomaly, though with significant highs occurring with this. The Hobbes Zone is marked by a small but strong resistivity high over the mineralized strongly silicified intrusives there. This zone was drilled in 2008 (holes ZY08-07 to 11), and returned values up to 0.44% Cu and 0.32g/t Au over 158.95m in hole ZY08-09. A number of other strong highs occur to the southwest of this on the south side of Hobbes Knob and towards Red Canyon Creek. Hole ZY08-12 targeted a resistivity-magnetic high and encountered hornfels with dykes and returned an interval of 99.0 metres of 0.11% Cu. A much larger 300 metre wide strong resistivity high occurs 400 metres downhill (southwest) of this. Silicified sediments have been observed in this area. Two small strong resistivity highs are noted in the FM Zone; one within the sericite-pyrite altered FM intrusive and another in sediments outside of the chargeability high, but still with the FM copper-gold soil anomaly.

Results from the 2008 ground magnetic survey correlated well with those of the 2004 aeromagnetic survey, Zymo ridge is a relative magnetic low which is flanked by strong highs. Numerous discrete magnetic highs are caused by intrusive rocks which may or may not carry copper mineralization.. The quartz-magnetite altered Hobbes diorite porphyry is a good example of this. The FM showings are apparent as a strong magnetic high.

The strong magnetic high that occurs northeast of the Red Canyon Creek drainage underlies both the RD and URC Zones shows well on both the airborne and ground surveys. At RD, auriferous base metal veins, sericite-pyrite altered sediments and dykes point towards the existence of a large buried intrusive. A magnetic low crosses westerly across the southern boundary of the property and most likely demarks the boundary with the Hazelton Group volcanics to the southwest.

Hobbes Zone Discussion

The Hobbes Zone is centered on a topographic high known as Hobbes Knob and is underlain by altered and hornfelsed sediments and lesser volcanics intruded by locally altered and mineralized intermediate dykes and larger intrusive bodies. A 1.5 by 1.5 kilometre copper and gold in soil geochemical anomaly surrounds the knob, and the highest chargeabilities encountered on the property, over 100mV, occur in the centre of the zone, under the knob. The zone is located four kilometres west of the FM intrusive. This area was discovered in 2007 during follow-up of strong magnetic highs identified in the 2004 airborne survey. Old flagging and broken outcrops indicate that this area had been visited in the past, but no work was recorded.

Some regional government maps show the Hobbes Zone to be located on a northwest trending fault contact between the Skeena Group sediments and Hazelton Group sediments. This inferred contact roughly coincides with the observed geology on Zymo Ridge; weakly altered sediments, dominated by cobble conglomerates to the north, and a southern unit which contains the chargeability high, numerous intrusions, strong alteration, and all of the known mineralization on the property.

The best mineralization yet discovered on the property, the Hobbes Showings, are located near the north edge of the Hobbes Zone where surface samples have returned up to 0.86% Cu and 0.65g/t Au. All of the 2008 drilling was done in the Hobbes Zone, and mineralization was encountered in each of the holes. The first five holes, ZY08-07 to 11, targeted the Hobbes Showing, and ZY08-12 was collared one kilometre south on the south side of Hobbes Knob. Highlights of the drilling include 72.0 metres of 0.72% Cu and 0.54g/t Au from ZY08-09, and 158.95 metres of 0.31Cu and 0.21g/t Au from ZY-08-10. Results from the 2008 drilling are given below.

Table 4: 2008 drill results

Zymo 2008 drill results						
Hole	from (m)	to (m)	Length (m)	Cu %	Au g/t	Notes
ZY08-07	3.05	252.98	249.93	0.2	0.14	entire hole
Includes	116.00	233.00	114.00	0.27	0.19	
Includes	119.00	182.00	66.00	0.33	0.20	
Includes	119.00	155.00	36.00	0.45	0.33	
ZY08-08	3.05	237.74	234.69	0.2	0.12	entire hole
Includes	51.00	111.00	60.00	0.39	0.26	
Includes	51.00	78.00	27.00	0.43	0.3	
And	96.00	111.00	15.00	0.56	0.35	
ZY08-09	3.05	256.02	252.97	0.32	0.23	entire hole
Includes	3.05	162.00	158.95	0.44	0.32	
Includes	3.05	90.00	86.95	0.65	0.49	
Includes	15.00	87.00	72.00	0.72	0.54	
ZY08-10	3.05	266.70	263.65	0.22	0.14	entire hole
Includes	3.05	162.00	158.95	0.31	0.21	
Includes	18.00	75.00	57.00	0.43	0.32	
ZY08-11	6.10	259.08	252.98	0.11	0.07	entire hole
Includes	6.10	153.00	146.90	0.16	0.1	
ZY08-12	3.05	281.94	278.89	0.065	0.035	entire hole
Includes	51.00	150.00	99.00	0.11	0.05	

The Hobbes Showing is located in the northern part of the zone and is comprises a core of chalcopyrite-bearing quartz-magnetite (potassic) altered diorite porphyry dykes(?) that lie within a large area of hornfelsed and variably sericite-silica-chlorite altered sediments and possible volcanics. The surface area of the largest mineralized intrusive is 300 by 150 metres and has been traced for 200 metres in drill core. The altered diorite porphyry here shows up well on resistivity and magnetic plots and is located within an embayment on the north side of the highest chargeability. Outcrops assay as high as 0.86% Cu and 1.1g/t Au.

As seen in drill core, the diorite porphyry is made up of a grey/green/pink groundmass (depending on the alteration) with 30-40% plagioclase laths 2-4mm in size. The 5-10% mafics have generally been altered to chlorite, though local unaltered coarse hornblendes were noted in the drill core. The porphyry has been strongly altered with quartz and magnetite, both occurring as veins and stringers, and as pervasive flooding. The magnetite often contains significant fine disseminated chalcopyrite. Impressive quartz stockworks are common with up to three directions of veining with the strongest orientation being east-west trending, moderately south dipping. Zones of green sausserite alteration were common in drill core. This may be a later event as it appears to remove the magnetite, though the quartz and sulfides, thankfully remain behind. Much of the core has a pink colour due to a combination of hematite (from magnetite), and local pink k-feldspar alteration around fractures. Similarly altered and mineralized diorite porphyry dykes are common around the main body and are still well mineralized in holes ZY08-07 to 10, but in ZY-08-11, on the southeast side of the main intrusive, alteration and mineralization is weaker.

As seen in drill core, host rock to the altered diorite porphyries are fine clastic sediments that have been very strongly altered with biotite, chlorite, local silicification, sericite and local magnetite. Most of the original textures have been destroyed and some of the rocks have been completely hornfelsed. Intervals of dark green chloritic rocks may be volcanics.

Along with the diorite porphyry dykes mentioned above, strongly chlorite-biotite altered fine diorite dykes are also common. These country rocks contain more pyrite than chalcopyrite, though they can still carry copper values over 0.3%, as noted in both the drill holes, and in surface exposures.

Chalcopyrite occurs as stockwork and fine disseminations and in quartz veins in the altered diorite porphyry and the adjacent sediments. Hole ZY08-09 contains chalcopyrite veins up to 1cm. Pyrite is also present in the diorite porphyry, but generally in lower quantities than chalcopyrite. Molybdenite occurs throughout the diorite porphyry and surrounding rocks, usually as local specks in quartz veins. The Hobbes Zone has copper-gold ratio of 1% Cu to 0.8g/t Au. The best mineralization occurs in the altered diorite porphyry and the adjacent altered country rocks, though long intervals of >0.1% Cu was encountered in the altered sediments in drill core and in surface exposures.

In Hobbes Creek, 125 metres west of ZY08-07, variably silicified, chloritic rocks returned values over 0.1% along 275 metres in a north-south section. The strong alteration makes identification difficult, but it is thought that diorite(?) intrusives, sediments and volcanic rocks occur here. The highest copper values from here are 0.33% Cu and 0.18g/t Au, reflecting a higher copper-gold ratio than in the altered diorite porphyry tested in the 2008 drilling. This area is a strong target for future drilling.

North of the mineralized zone in Hobbes Creek, copper values drop off rapidly into strongly sericite-pyrite altered siltstones with local pyrite and quartz stockworks. East-west trending, moderately south dipping fracture zones with locally abundant pyrite and pyrhotite are also found. Outcrops of unaltered cobble conglomerate are found 250 metres north of the altered siltstones. The cobble conglomerates are part of the unaltered northern lithological unit on the Zymo Property, while the altered siltstones are part of the altered southern unit, which contains numerous intrusions, the chargeability high, and the known mineralization.

Fresh, unaltered diorite bodies to 50 metres across occur on the north and west side of the area, and post-mineral feldspar porphyry dykes were also noted in core. Fracture zones with disseminated chalcopyrite running 2317ppm Cu and 39ppb Au occur in one of these, located 250 metres west of Hobbes Creek.

Hole ZY08-12 was collared one kilometre south of the Hobbes Showing on the south side of Hobbes Knob, and targeted a strong magnetic high in the vicinity of chalcopyrite bearing chlorite-magnetite altered diorite float/subcrop showings. The hole encountered strongly hornfelsed sediments and local altered dykes and returned 99 metres of 0.11% Cu. The soils in this area on the south side of Hobbes Knob are weakly to moderately anomalous in copper and gold.

The rest of the Hobbes Zone area is underlain by siliceous sediments/silicified siltstones and hornfelsed sediments and local variably chlorite/magnetite altered dykes. Anomalous copper values occur throughout the zone with values of >0.1% Cu occurring in local zones of very high pyrite content. The hornfels contains 1-2% disseminated pyrite and local pyrhotite. The main copper and gold geochemical anomaly of the Hobbes Zone is weaker over the top of Hobbes Knob, but strong copper in silt anomalies encircle the knob, suggesting that it is a weakly mineralized cap, with mineralization underneath. The highest chargeability values of the 2008 programme, over 100mV, are located under the top of the knob.

The Hobbes Showings appear to consist of a dyke swarm of potassic altered and mineralized diorite porphyry bodies within strong mineralization in the adjacent altered sediments. Strong copper, gold and molybdenum geochemistry occur across an area 1.5 by 1.5 kilometres, with the best numbers occurring around the periphery of Hobbes Knob which appears to be a weakly mineralized cap. Strong copper in silt anomalies on the south and east side of the zone have yet to be explained despite extensive prospecting. The lack of the auriferous base metals veins and high zinc contents common in FM Zone area, along with the abundance of strong molybdenum in soils, and rocks, indicate that the area is proximal to large potentially mineralized porphyry system.

FM Zone Discussion

The FM Zone is a two by two kilometre strongly sericite-pyrite altered porphyritic, dioritic feldspar porphyry which is surrounded by similarly altered sediments. Grabs of porphyry type mineralization from across the zone has returned copper values up to 0.92% and gold to 0.48g/t, and base metal veins from the north and east side of the intrusive carry gold values to over 7g/t. This was the only known mineralization on the property prior to 2007.

Freeport Copper Company drilled 1448 metres in six holes here in 1999. The programme was geological in nature, seeking to determine whether the alteration system reflected a porphyry system that would be in line with Freeport's requirements. The holes were widely spaced and did not specifically target known mineralization. Five of the six holes encountered phyllic altered diorites and breccias with anomalous copper values, including 285.97 metres of 467ppm Cu in hole ZY-99-03. The sixth hole; ZY-99-04, encountered black shale and was not sampled. Its location, only 175 metres northwest of the FM showing indicates a NNE trending fault here.

The two most significant showings here are the FM and 2Bob. The FM Showing consists of silicified sericite-pyrite altered intrusive adjacent to a fault contact. Pyrite content is up to 2%. Chalcopyrite and malachite are rare, but a chip sample across the zone in 2007 returned 0.13% Cu and 0.23g/t Au over 85 metres, This showing shows as a prominent magnetic high. The best results were from near the fault contact, to 0.24% Cu. Aside from ZY-99-04, the closest drill hole to this showing is ZY-99-01, 350 metres east.

The 2Bob showing is located 650 metres southeast of the FM, and consists of a northwest trending silicified structural zone which contains chalcopyrite and local bornite with grades up to 0.92% Cu. The surrounding rocks are variably silicified and run up to 0.23% Cu. The nearest drill holes are ZY-99-03, 550 metres west, and ZY-99-05, 560 metres southeast. Both showings are marked by very strong iron-manganese staining. Neither of these showings have been tested by drilling.

Auriferous base metal veins are known from the northeast and east parts of the FM Zone, near the edges of the intrusive. The FM and surrounding area is anomalous in zinc, lead and antimony as well as copper and gold. The presence of the base metal veins and the zinc and lead geochemistry indicate that this area may be above the zone of mineralization.

Table 5: Summary of 1999 Drilling Results, FM Zone

Hole #	Mineralized Intervals					
	% of core sampled	From (m)	To (m)	interval	Cu (ppm)	Au (ppb)
ZY-99-01	99.5	3.35	307.77	304.42	243	27
ZY-99-02	62.7					
ZY-99-03	76.3	12.2	298.17	285.97	467	71
	including	12.2	35.98	23.8	0.14%	214
ZY-99-04	0	not sampled				
ZY-99-05	34.9					
ZY-99-06	93.7	11.59	255.49	243.9	375	43
	including	29.88	41.16	11.3	0.14%	99

RD Zone Discussion

The RD Zone is located 2.5 kilometres southwest of the FM Zone drilling above Red Canyon Creek. It consists of auriferous base metal veins, up to one metre wide and over 100 metres in length, phyllic altered sediments and dykes, and anomalous Cu, Au, Zn, Pb, As, and Sb in rocks and soils. These features lie on the southwest edge of the chargeability high and on the northeast edge of a strong ground-airborne magnetic anomaly, possibly indicating proximity to a mineralized intrusive at depth.

URC Zone Discussion

The URC Zone is located two kilometres west of Hobbes and is defined by anomalous Cu, Au, Mo, As and Ga in rocks and soils and is underlain by the airborne magnetic high that runs along Red Canyon Creek. Outcrop is scarce in the area but chalcopyrite has been found in diorite dykes and mineralized float, running up to 0.31% Cu and 0.15g/t Au from altered intrusive float.

2008 Reconnaissance Work Discussion

The bulk of the 2008 work was directed at Zymo ridge, and the reconnaissance work consisted of four reconnaissance soil lines in three areas. Two of these lines were on the north side of Mulwain Creek following up a weak copper in silt anomaly and the other two were in the south end of the property following up small discrete airborne magnetic highs. Nothing of note was found in any of these lines.

Conclusions and Recommendations

The Zymo property is underlain by clastic sediments of the Skeena, Bowser and Hazelton Groups, which have been intruded by intrusive rocks of granite and diorite composition. Copper-gold porphyry mineralization has been found in a number of locations on the property, and four zones of mineralization have been discovered so far, Hobbes, FM, RD and URC. A ground geophysical programme in 2008 revealed a large chargeability anomaly that runs for six kilometres along Zymo ridge, and is up to three kilometres wide, with the mineralized zones lying at its edges.

The best mineralization to date has been found in the Hobbes Zone where potassic altered diorite porphyry was the target of a six hole 1554 metre drill program in September. All of the holes encountered mineralization including 0.72% Cu and 0.54g/t Au over 72.0 metres in hole ZY08-09, and 0.31% Cu and 0.21g/t Au in hole ZY08-10.

The next phase of exploration on the Zymo property should consist initially of expanding the 2008 ground geophysical survey. The southwest side of Zymo Ridge would be the main target area, over the RD and URC Zones, which already have chargeability, resistivity and magnetic anomalies from the single lines that were emplaced there in 2008, and also have associated multi-element geochemical anomalies and mineralized outcrop and float. Two hundred metre spaced lines should be run over these two zones. Additional lines should cover the area between these two zones, possibly at a wider spacing, depending on budgets. The area between the two existing grids on the top of Zymo Ridge should also be infilled. Interpretations of the geophysical data will be an ongoing effort as more is learned about the geology of the area. All of the soil lines should be soil sampled as well.

Mapping and prospecting should continue, again focusing on the Red Canyon Creek area around and between the RD and URC Zones. Though the north side of the Hobbes Zone has been well mapped and sampled, much more work needs to be done in other parts of the zone.

Drilling should be an essential part of the program, targeting new anomalies as well as following up the impressive 2008 results from the Hobbes Showing, and testing geological, geochemical and geophysical targets in other areas. Future reconnaissance work should be directed to the area southwest of Red Canyon Creek as no work has been done here so far.

Statement of Expenditures

Table 6: Zymo Project: 2008 Expenditure Statement:

Professional Fees:

R. Johnston	115½ days @ \$680/day	\$78,540.00	G
G.L. Garratt	14 days @ \$680/day	9,520.00	G

Field Personnel Fees:

R. Dennett	18 days @ \$445/day	8,010.00	G
G. Charbonneau	½ day @ \$420/day	210.00	G
J.P. Charbonneau	31 days @ \$420/day	13,020.00	G
E. Stewart	78 days @ \$410/day	31,980.00	G
M. Stewart	27 days @ \$410/day	11,070.00	G
K. Syme	17 days @ \$410/day	6,970.00	G
P. Charbonneau	70 days @ \$385/day	26,950.00	G
S. Salter	30 days @ \$360/day	10,800.00	G
E. Walker	89 days @ \$350/day	31,150.00	G
M. Kozenko	66 days @ \$310/day	20,460.00	G
J. Jackson	19 days @ \$310/day	5,890.00	G
M. West	42 days @ \$310/day	13,020.00	G
E. Williams	64 days @ \$310/day	19,840.00	G
M. Williams	25 days @ \$310/day	7,750.00	G
L. Williams	10 days @ \$310/day	3,100.00	G
K. Charbonneau	72 days @ \$270/day	19,440.00	G

Rentals:

1 Rock Saw	80 days @ \$20/day	1,600.00	G
Printer	87 days @ \$5/day	435.00	G
9 Handheld Radios	87 days @ \$5/day each	3,915.00	G
2 Generators	91 days @ \$50/day each	9,100.00	G
Camp	91 days @ \$50/day	4,550.00	G
Kitchen / Dry Equipment	91 days @ \$150/day	13,650.00	G
Truck (Johnston)	18 days @ \$80/day	1,440.00	
Truck (Val Geo Tech)	27½ days @ \$80/day + PST	2,354.00	
Truck (M Williams)	5 days @ \$80/day	400.00	
Truck (P Charbonneau)	29 days @ 80/day	2,320.00	
Truck (Salter)	6 days @ \$80/day	480.00	
Truck (Jackson)	1 day @ \$80/day	80.00	
Truck (E Stewart)	33 days @ \$80/day	2,640.00	
Truck (Kozenko)	3 days @ \$80/day	240.00	
Truck (Walker)	31 days @ \$80/day	2,480.00	
Truck (M Stewart)	11 days @ \$80/day	880.00	
Truck (Garratt)	3 days @ \$80/day	240.00	
GPS (P Charbonneau)	43 days @ \$5/day	215.00	
Generator (JP Charbonneau)	7 days @ \$10/day	70.00	
Chainsaw (Kozenko)	28 days @ \$25/day	700.00	
Chainsaw (Jackson)	11 days @ \$25/day	275.00	

R. J. Johnston, P. Geo.

Chainsaw (West)	19 days @ \$25/day	475.00
Chainsaw (JP Charbonneau)	5 days @ \$25/day	125.00
Chainsaw (K Charbonneau)	2 days @ \$25/day	50.00
Transportation:		
Helicopter	215.7 hours @ \$1,102.22	237,749.30
Scheduled Flights		1,021.49
Travel Expenses:		
Fuel:		
15,497.34		
Analyses:		
Assay	2,224 samples @ \$22/sample	48,937.64
	Petrographic	1,094.02
Drilling:		
168,309.44		
Sub Contractor:		
	Geological	4,050.00
	Geophysical Survey (IP/Mag)	52,792.62
Field Equipment:		
33,138.16		
Communication:		
	Telephone	1,325.93
	Postage	21.10
Freight:		
74.49		
Miscellaneous:		
186.50		
Food:		
19,770.07		
Vehicle Expense:		
40.11		
Accommodation:		
32,197.79		
Warehouse / Storage:		
1,600.00		
<hr/>		
Sub Total		\$988,790.97
GST on \$350,970.00		17,548.50
<hr/>		
TOTAL		\$1,006,339.40

(G denotes items carrying GST charges which are added at the bottom)

R. J. Johnston, P. Geo.

Statement of Qualifications

I, R.J.Johnston, am a graduate of the University of Saskatchewan with a B.Sc. (Advanced) 1982, in Geological Science.

I am a member of the Association of Professional Engineers and Geoscientists of the Province of BC (P.Geo.), registration number 19253.

I have practiced my profession since graduation in Western Canada, Mexico and Central America.

I, R.J.Johnston, supervised the exploration programme outlined in this report and personally carried out mapping, prospecting and rock sampling, and logging of drill core.

Dated this 4th day of February, 2009.

R.J.Johnston P.Geo.

R. J. Johnston, P. Geo.

References

Day, R.C., December 01, 1996: Zymo #1-8 Claims, Reconnaissance Prospecting Report, Omineca Mining Division, BC, AR# 24924.

Day, R.C., November 01, 1997: Zymo #1-10 Claims, Reconnaissance Geological and Geochemical Report, Omineca Mining Division, BC, AR # 25412.

Day, R.C., August 31, 1998: Zymo #7-10 Claims, Reconnaissance Geological & Geochemical Report, Omineca Mining Division, BC, AR # 25820.

Garratt G.L., September 25, 2007: Zymo Property, Executive Summary for Eastfield Resources Ltd.

Jamieson, M.D., September 30, 1991: Geological and Geochemical Sampling Report on the Red 1 and 2 Claims, Omineca Mining Division, BC, by Taiga Consultants Ltd. for Skeena Resources Limited; AR # 21723.

Johnston, R.J.; February 15, 2008: Assessment Report on Exploration at Zymo Property, Omineca Mining Division

Klassen, R., November 8, 1988: Assessment Report on 1988 Work, Calvin Claim, Red Canyon Creek, Omineca M.D., AR # 18050.

Nelson, F.J., January 24, 2000: Zymo # 7-17 Claims, Core Drilling Program Report, Omineca Mining Division, BC, AR # 26152.

Robertson, K., May 5, 2005: Technical Report For The Zymo Property for NDT Ventures Ltd..

Visage, D., December, 2005: Geophysical Report, Zymo Property for NDT Ventures Ltd.

PROPERTY: ZYMO		Loc Method; GPS		dip tests							
Hole # ZY-08-07		UTM E 562810		depth	corrected dip						
Depth (m); 252.98		UTM N 6077713		252.98	-63			Start Date: Sept 4/08			
Core size; NQ		Azimuth: 030°						Completion: Sept 5/08			
Drilled by; Driftwood Diamond Drilling		Inclination: -59°		GRID W	137+75W			Logged By: Johnston			
NOTES;		Elevation: 1275m		GRID N	105+78N			Date logged; Sept 10-15/08			
ZY-08-07											
depth (m)	description	litho code	sample #	from	to	length (m)	rec %	Mo ppm	Cu ppm	Au ppb	
from	to										
0.00	3.05	casing	DPmq	933001	3.05	5.08	2.03	70	77	1833	138
				933002	5.08	7.80	2.72	101	128	1103	53
3.05	108	gy-pk sil-mgt-ksp alt diorite porphyry		933003	7.80	11.00	3.20	93	2	591	36
		gy groundmass with zoned 2-4mm plag felds composing 20-30% of the rock		933004	11.00	14.00	3.00	98	32	891	50
		1-2mm mafics gone to chl; sporadic coarse weakly altered hb's to 7mm occur to 50m		933005	14.00	17.00	3.00	100	3	869	46
		minor ep		933006	17.00	20.00	3.00	97	2	790	48
		variable pervasive sil'n; locally strong zones associated with fine pervasive mgt alteration		933007	20.00	23.00	3.00	101	7	1285	73
		fine cc on frax with wh, d gy clay		933008	23.00	26.00	3.00	97	20	1717	111
		pink zones due to staining from mgt gone to hematite.		933009	26.00	29.00	3.00	102	9	1049	65
		mgt as pervasive fine or coarse disseminations, distinct veins, generally associated with cp		933010	29.00	32.00	3.00	104	2	1662	111
		cp minor; inc with mgt, as v fine disseminations, local veins; inc with inc mgt, sil'n; py=cp overall; more py on frax		933011	32.00	35.00	3.00	97	6	2065	128
		qtz vns to 1 cm occur throughout; most are 1-2mm d gy vns with cp on the centre-line, these appear to be more common in the suas alt zones?		933012	35.00	38.00	3.00	106	2	1285	102
		local zones, to 3m, of green sausserite alteration; lt gn gm, dark apple green alt felds; no mgt; local cp, diss, frax; make up 10-20% of interval		933013	38.00	41.00	3.00	98	3	1329	99
		local mo to 30m; on frax & in qtz-carb vns in both gy-pk, and gn alt diorite porphyry		933014	41.00	44.00	3.00	100	5	2039	113
				933015	44.00	47.00	3.00	100	3	3251	262
		24.8m; 10cm 45CA wh carb vn		933016	47.00	50.00	3.00	101	2	2073	150
		30-32m; inc sil'n; ep on frax		933017	50.00	53.00	3.00	93	3	1225	68
		34-36.5m; local 1-2mm gy qv's with cp on centreline		933018	53.00	56.00	3.00	96	2	1306	92
		37.4-38.75.; feldspar porphyry dyke; gn gm; scattered wh felds to 7mm; sl magnetic; minor py; no sil'n		933019	56.00	59.00	3.00	100	3	982	60
		41-72m; mod sil'n; cp in local 1-2mm gy qv's, on frax, diss with mgt; local py on frax		933020	59.00	62.00	3.00	97	5	1185	70
		45.0m; 0.5m of d gn chl, pk ksp? alt; with cp stwk		933021	62.00	65.00	3.00	100	9	1884	159
		49.5-55m; gn-buff saus alt zone; sil'n same as above; abund carb vns with local vfg py; local red hem (after mgt?) specks in qv's; minor cp, py		933022	65.00	68.00	3.00	106	2	1559	116
		56.9-59m; lt gn saus alt zone; as above; vfg mgt with fine cp		933023	68.00	71.00	3.00	100	4	2086	131
		64-94m; local pk ksp alt haloes around frax; alter gm but not (plag) felds; also local discrete pk vns		933024	71.00	77.00	6.00	100	5	1628	142
		74m; 2mm lt bn anhydrite? vn		933026	77.00	80.00	3.00	100	2	1371	90
		79-86.5m; inc sil'n accompanied by inc fg mgt gives dark grey colour; also inc 1-2mm gy qv's with cp, inc cp as diss, minor stockworks; local py on frax		933027	80.00	83.00	3.00	101	1	1795	131
		86.3m; 0.3m zone with 5% vfg diss py		933028	83.00	86.00	3.00	100	2	2073	160
		86.6m; 2m zone of gn saus alt; 1-2mm gy qv's with cp		933029	86.00	89.00	3.00	107	3	2564	247
		93-108m; d gy sil'n fg mgt alt inc; cp inc to 0.5%, diss and on frax; also inc 1-2mm gy qv's with cp		933030	Standard CDN-CGS-6						
		94-108m; common pk ksp stain to gm; local pk ksp vns to 1cm		933031	89.00	92.00	3.00	101	18	1060	66
				933032	92.00	95.00	3.00	96	2	1052	89
				933033	95.00	98.00	3.00	104	2	1262	96
				933034	98.00	101.00	3.00	102	2	1827	145
				933035	101.00	104.00	3.00	101	2	1460	111
				933036	104.00	107.00	3.00	98	2	1720	148

PROPERTY: ZYMO		Loc Method; GPS		dip tests										
Hole # ZY-08-08		UTM E	562809	depth	corrected dip									
Depth (m); 237.74		UTM N	6077709	no test						Start Date: Sept 6/08				
Core size; NQ		Azimuth: 210°								Completion: Sept 8/08				
Drilled by; Driftwood Diamond Drilling		Inclination: -59°		GRID W	137+75W					Logged By: Johnston				
NOTES;		Elevation: 1275m		GRID N	105+74N					Date logged; Sept 16-20/08				
ZY-08-08														
depth (m)		description				litho code	sample #	from	to	length (m)	rec %	Mo ppm	Cu ppm	Au ppb
from	to													
0.00	3.05	casing												
3.05	14.1	gy-pk ksp-sil-mgt alt diorite porphyry				DPmq	933088	3.05	6.00	2.95	75	29	3431	199
		gy-pk gm; pk due to ksp alt / mgt gone to hem					933089	6.00	9.00	3.00	99	5	2153	157
		30-40% wh-gn felds (plag)					933090	Standard CDN-CGS-6						
		local zones with sporadic coarse (to 8mm) hb phenos; wk chl alt					933091	9.00	12.00	3.00	100	2	581	52
		local d gy sil-mgt alt zones make up 30% of interval					933092	12.00	15.00	3.00	96	9	746	52
		local gn saus alt zones xcut sil-mgt alt												
		cp, diss stringers in sil-mgt alt; minor py												
		local wh carb vns												
14.1	19.85	gn saus alt diorite porphyry				DPS	933093	15.00	18.00	3.00	96	6	1772	100
		lt gn gm with apple gn saus alt felds; local sil'n					933094	18.00	21.00	3.00	97	14	1109	61
		local mgt vns												
		minor py, tr cp; minor 1-2mm gy qv's with cp												
		15.0-15.8m ; crush zone; alt diorite porphyry frags in gn clay; 1cm 10CA bk qv at bottom												
19.85	33	gy-pk ksp-sil-mgt alt diorite porphyry				DPmq	933095	21.00	24.00	3.00	87	2	1549	96
		as above; coarse hb's continue to 25m					933096	24.00	27.00	3.00	97	26	840	40
		wk-mod mgt flooding; local sil'n					933097	27.00	30.00	3.00	95	4	1346	88
		minor gn saus alt zones to 2m; 1-2mm gy qv's with cp more common here					933098	30.00	33.00	3.00	95	2	881	58
		minor cp diss with mgt; in 1-2mm gy qv's; minor py, tr mo												
33	50.8	gn saus alt diorite porphyry				DPS	933099	33.00	36.00	3.00	100	4	1061	65
		as above					933100	36.00	39.00	3.00	104	2	1514	86
		abund 1-2cm low CA carb vns with vfg muddy py					933101	39.00	42.00	3.00	88	4	1119	46
		minor 1-2mm gy qv's; minor diss py, cp					933102	42.00	45.00	3.00	111	7	895	53
		43-44.7m; soft gn clay around low CA frax; wh carb vns, with vfg muddy py					933103	45.00	48.00	3.00	102	6	566	27
							933104	48.00	51.00	3.00	100	64	963	46
50.8	57	gn saus-sil alt diorite porphyry				DPS	933105	51.00	54.00	3.00	104	12	5308	336
		as saus alt zones above, but v sil'd					933106	54.00	57.00	3.00	100	16	4501	300
		strong stwk of 1-3mm gy qtz vns with cp; also common mgt vns, local mgt flooding												
		cp to 0.5%; minor py												
		50.8-52.0m; v broken; vfg py to 5%												
		local red hem in mgt vns												
57	69.5	gy-pk ksp-sil-mgt alt diorite porphyry				DPmq	933107	57.00	60.00	3.00	90	21	3015	237
		v sil'd; local d gy mgt flooded zones; minor gn saus alt					933108	60.00	63.00	3.00	99	5	3009	178
		abund 1-2mm gy qv's with cp; locally a stwk					933109	63.00	66.00	3.00	100	3	4135	269
		cp to 0.5% in qv's, fg diss in mgt flooded zones; minor py, tr mo					933110	66.00	69.00	3.00	100	2	4135	294
		65-69.5m; cp to 1%												
69.5	73.5	sil'd gy siltstone				ST	933111	69.00	72.00	3.00	95	3	4457	326
		lt-dk gy; v broken; local strong mgt					933112	72.00	75.00	3.00	100	4	4878	371

ZY-08-08											
depth (m)		description	litho code	sample #	from	to	length (m)	rec	Mo	Cu	Au
from	to							%	ppm	ppm	ppb
		1-2mm gy qv's with local cp; py on frax									
73.5	78	gy-pk ksp-sil-mgt alt diorite porphyry strong sil'n; d gn chl-mgt flooded zones with 1% cp local coarse hb's pk from ksp alt? abund low CA qv's with cp	DPmq	933113	75.00	78.00	3.00	100	7	5789	433
78	80.5	gn saus-sil alt diorite porphyry local pk-gy ksp-mgt-sil alt zones as well gy clay alt frax, locally with vfg muddy py local mo	DPs	933114	78.00	81.00	3.00	100	24	1225	91
80.5	88.8	gy-pk ksp-sil-mgt alt diorite porphyry mgt as diss clots, flooding, in qv's local 1-2cm pk ksp vns with minor cp cp locally to 1%; local py on frax coarse hb's gone weakly to chl with minor cp 82.5m; 0.5m of v intense mgt-cp alt gn saus in bottom 2m	DPmq	933115	81.00	84.00	3.00	100	12	2725	149
				933116	84.00	87.00	3.00	100	10	2234	119
88.8	93.9	ser alt gy siltstone v broken; locally abund wh, dk clay frax; vfg py with dk clay local diss cp in upper 2m local sil'n with minor mgt, cp minor 1-2mm gy qv's with cp; minor py on frax	ST	933117	87.00	90.00	3.00	10	4	1760	110
				933118	90.00	93.00	3.00	100	5	3072	161
93.9	96	gn saus-sil alt diorite porphyry soft; local mgt specks; minor 1-2mm gy qv's with cp local pk ksp alt to bottom	DPS	933119	93.00	96.00	3.00	100	4	1366	69
				933120	Standard CDN-CGS-6						
96	105.5	dk gn-gy hornfels v broken; cc on frax; weakly sil'd to 98m dk gn chl-mgt alt (volc?) from 96-101; diss, vn cp to 1% 97m; 10cm 20CA diorite porphyry dyke; alongside 2cm pk qtz-kfeld dyke 101-105.5m; minor cp; diss with mgt, in qv's 102-104m; qv stwk with local cp, py	HF	933121	96.00	99.00	3.00	100	5	6975	419
				933122	99.00	102.00	3.00	94	7	9588	670
				933123	102.00	105.00	3.00	98	31	4504	246
105.5	110.3	gn saus-sil alt diorite porphyry wh gy calc clay on frax; minor diss cp in wh sil'd haloes to qv's minor diss py	DPs	933124	105.00	108.00	3.00	91	31	3801	219
				933125	108.00	111.00	3.00	75	51	3168	178
110.3	133.7	dk gy siltstone as 88.8-93.9m; v broken; no sil'n local lt bn biot? alt zones; biot/Fe carb? to 124m common wh-gy qtz-carb vns with local py, cp, tr mo 111.5m; 0.3m gn suas alt diorite porphyry dyke v broken to 130m	ST	933126	111.00	114.00	3.00	96	96	1248	67
				933127	114.00	117.00	3.00	83	39	934	34
				933128	117.00	120.00	3.00	92	62	710	40
				933129	120.00	123.00	3.00	96	88	1047	54
				933130	123.00	126.00	3.00	96	43	781	45
				933131	126.00	129.00	3.00	100	59	1198	111
				933132	129.00	132.00	3.00	97	43	670	46
				933133	132.00	133.70	1.70	100	36	811	47

PROPERTY: ZYMO		Loc Method: GPS		dip tests						
Hole # ZY-08-09		UTM E	562942	depth		corrected dip				
Depth (m); 256.03		UTM N	6077732	256.03		-62		Start Date: Sept 8/08		
Core size; NQ		Azimuth: 027°						Completion: Sept 11/08		
Drilled by; Driftwood Diamond Drilling		Inclination: -59°		GRID W	136+70W			Logged By: Johnston		
NOTES;		Elevation: 1282m		GRID N	106+55N			Date logged; Sept 20-23/08		
ZY-08-09										
depth (m)	description		litho code	sample #	from	to	length (m)	rec %	Cu ppm	Au ppb
from	to									
0.00	3.05	casing								
3.05	18.2	gn saus alt diorite porphyry	DPs	933169	3.05	6.00	2.95	42	3137	206
		gn gm with apple gn felds; hb's locally gone to chl, also alt to wh-buff mineral		933170	6.00	9.00	3.00	100	1558	118
		local mgt; common 1-2mm gy qv's		933171	9.00	12.00	3.00	100	3598	283
		cp in qv's, in mgt clots, minor diss, to 0.5%; minor py		933172	12.00	15.00	3.00	100	2978	212
		3.05-4.0m; crackle bx; abund fine bk chl? frax, veins		933173	15.00	18.00	3.00	99	4726	346
		3.05-11.5m; mod soft clay alt; wh clay on frax;								
		15.5-18.2m; local pk ksp alt gm around frax; felds still gn								
18.2	21.5	dk gy strongly sil-mgt alt diorite porphyry	DPmq	933174	18.00	21.00	3.00	105	5091	410
		dk gn gm with patches of dk gy mgt flooding								
		strong sil'n; abund 1-2mm gy qv's								
		cp in qv's, diss with mgt, frax								
		sharp 45CA lower contact								
21.5	24.1	sil'd sltn/mylonite?	MY	933175	21.00	24.00	3.00	96	2993	223
		lt gn-bn vfg, sil'd; abund fine bk ser-py frax								
		23.5-24.1m; bk mgt flooding; qtz vns with cp								
24.1	31.9	gn sil-saus alt diorite porphyry	DPs	933176	24.00	27.00	3.00	101	6737	603
		abund 1-2mm gy qv's with cp, minor mo; 30CA most common direction		933177	27.00	30.00	3.00	100	5912	464
		local mgt; in clots and vns where; often gone to hem; minor py		933178	30.00	33.00	3.00	99	5317	367
31.9	39.25	dk gy strongly sil-mgt alt diorite porphyry	DPmq	933179	33.00	36.00	3.00	100	8259	584
		dk gy-gn mg; mgt as 1-5mm clots		933180	Standard CDN-CGS-6					
		v abund 1-2mm gy qv's with cp; 30CA most common orientation, biggest vns; tr mo		933181	36.00	39.00	3.00	106	7968	561
		diss cp in gm to 1%; local py on frax								
		36.5m; 0.5m of gn saus alt; gn-pk (ksp?) gm								
39.25	51.5	gn saus alt diorite porphyry	DPs	933182	39.00	42.00	3.00	97	5410	421
		apple gn felds in gn-pk gm; local pk from ksp alt dec after 42.5m to buff-gn gm		933183	42.00	45.00	3.00	98	7518	529
		variably sil'd; local dk gy mgt flooded intervals, local diss clots		933184	45.00	48.00	3.00	99	8960	626
		strong gy qv stwk with cp, local py		933185	48.00	51.00	3.00	102	6460	464
		cp in qv's, also in frax; diss in mgt flooding; to 0.2%								
51.5	61.5	dk gy sil-mgt alt diorite porphyry	DPmq	933186	51.00	54.00	3.00	102	9643	843
		dk gy mgt flooded; mod sil'n		933187	54.00	57.00	3.00	100	8708	730
		local zones with buff-gn, gn-pk gm as above		933188	57.00	60.00	3.00	115	15790	1093
		abund qv's cont; with cp		933189	60.00	63.00	3.00	85	9767	855
		cp in vns, diss, frax, locally to 1%								
		57m; v impressive cp								
61.5	88.5	gn-pk saus-ksp alt diorite porphyry	DPs	933190	63.00	66.00	3.00	96	11270	740
		gn saus alt gm with apple gn felds, gm alt locally overprinted with pk ksp alt; mod sil'n		933191	66.00	69.00	3.00	95	6031	473

ZY-08-10											
depth (m)		description	litho code	sample #	from	to	length (m)	rec	Mo	Cu ppm	Au
from	to							%	ppm	ppm	ppb
190.5	195.95	bn-gn hornfelsed sltn strong ser alt; local biot diss py to 0.5% 192-193m; 0.2% fine cp diss in strong biot alt zone	HF	933321	192.00	195.00	3.00	101	23.9	2212.6	138.8
195.95	199.17	bx zone v broken; alt ser-biot hornfelsed sltn as above, below, in gy clay matrix	BX	933322	195.00	198.00	3.00	101	56.4	1259.6	56.9
				933323	198.00	201.00	3.00	99	57.0	450.4	25.1
199.17	213.5	bn hornfelsed sltn abund wh clay, cc frax minor py, no qv's biot dec, chl inc after 207m; prob more dykes	HF	933324	201.00	204.00	3.00	100	17.4	633.0	26.5
				933325	204.00	207.00	3.00	99	10.4	393.5	17.7
				933326	207.00	210.00	3.00	97	9.0	493.1	15.0
				933327	210.00	213.00	3.00	102	17.6	522.3	14.9
213.5	224	gy-gn chl alt diorite porphyry 30% felds to 2mm abund wh carb vns 1-2% diss, frax py; local bk ser-biot patches to 2cm wk sil'n, no mgt 222-224m; buff bleached zone around 45CA shear; incl minor qv's with abund py 229m; minor pk ksp alt	DP	933328	213.00	216.00	3.00	97	11.9	575.3	17.7
				933329	216.00	219.00	3.00	105	20.2	405.7	20.7
				933330	Standard	CDN-CGS-6					
				933331	219.00	222.00	3.00	95	13.5	484.8	36.2
				933332	222.00	225.00	3.00	100	31.5	422.9	44.2
224	237.9	buff coloured lt gn ser-chl alt ss local biot alt; 1% py local sltn intervals	ST	933333	225.00	228.00	3.00	103	16.4	466.4	24.8
				933334	228.00	231.00	3.00	101	54.2	546.3	43.6
				933335	231.00	234.00	3.00	100	50.9	486.6	29.6
				933336	234.00	237.00	3.00	96	16.6	262.1	25.0
237.9	259.95	ser alt diorite 40-50% fine wh felds; minor ser, wk chl alt; no sil, mgt; 1-2% py locally strong dk ser-py frax 249-252m; gn chl, wk sil alt 254.5-256.5m; soft clay-ser alt, abund cc vns sharp 45CA lower contact	DK	933337	237.00	240.00	3.00	97	4.3	141.9	15.6
				933338	240.00	243.00	3.00	100	5.8	242.1	23.4
				933339	243.00	246.00	3.00	100	5.3	178.2	20.4
				933340	246.00	249.00	3.00	104	8.6	135.1	20.1
				933341	249.00	252.00	3.00	91	6.2	110.8	7.0
				933342	252.00	255.00	3.00	101	8.4	130.7	12.9
				933343	255.00	258.00	3.00	102	4.1	179.5	25.4
259.95	266.7	gy-pk alt sltn wk bn biot alt locally strong dk ser-py frax EOH	ST	933344	258.00	261.00	3.00	98	4.2	192.8	22.0
				933345	261.00	264.00	3.00	100	1.5	70.5	16.4
				933346	264.00	266.70	2.70	110	1.0	65.1	8.6

PROPERTY: ZYMO			Loc Method: GPS		dip tests					
Hole # ZY-08-11			UTM E	563043	depth	corrected dip				
Depth (m); 259.08			UTM N	6077610	259.08	-58	Start Date: Sept 14/08			
Core size; NQ			Azimuth: 037°				Completion: Sept 16/08			
Drilled by; Driftwood Diamond Drilling			Inclination: -59°		GRID W	135+22W	Logged By: Johnston			
NOTES;			Elevation: 1290m		GRID N	105+95N	Date logged; Sept 26-28/08			
ZY-08-11										
depth (m)		description	litho code	sample #	from	to	length (m)	rec %	Cu ppm	Au ppb
from	to									
0.00	6.1	casing	DPs	933347	6.10	9.00	2.90	57	1204	48
				933348	9.00	12.00	3.00	75	1492	87
6.1	18	dk gn chl-saus alt diorite porphyry		933349	12.00	15.00	3.00	73	1395	86
		gn gm; apple gn saus alt felds; local mgt		933350	15.00	18.00	3.00	98	1474	71
		hb's gone to white-buff mineral								
		cp in qv's, with mgt clots, minor diss; to 0.2%; minor py								
		3.05-4m; crackle bx; abund bk chl/biot? frax								
		3.05-11.5m; mod soft clay alt on frax								
		15.5-18.2m; local pk ksp alt gm; felds stay gn								
18	26.5	bn biot-chl alt diorite	DK	933351	18.00	21.00	3.00	97	1207	55
		strongly altered; can discern local felds, less than in diorite porphyry		933352	21.00	24.00	3.00	100	1072	49
		py to 1%; tr cp		933353	24.00	27.00	3.00	99	1360	63
		local gyp vns								
26.5	51	gn chl-biot alt diorite porphyry	DP	933354	27.00	30.00	3.00	84	1735	78
		gn mass gm; felds visible after 30m		933355	30.00	33.00	3.00	97	1732	103
		biot inc after 36m		933356	33.00	36.00	3.00	94	2070	88
		local mgt vns; local ep in frax, often with cp		933357	36.00	39.00	3.00	100	1589	67
		py to 2%; minor cp		933358	39.00	42.00	3.00	98	1882	89
		42-43m; bleached, broken		933359	42.00	45.00	3.00	96	1882	90
		43-51m; inc chl alt, minor mgt flooding with minor diss cp, py to 1%		933360	Standard CDN-CGS-6					
				933361	45.00	48.00	3.00	103	2012	95
51	85.3	ser-biot-chl alt siltstone (hornfels)	HF	933362	48.00	51.00	3.00	106	1878	102
		broken core; no mgt		933363	51.00	54.00	3.00	95	1080	66
		chl disappear by 60m		933364	54.00	57.00	3.00	92	1552	101
		dk gy ser-py stwk; py to 1%; tr cp		933365	57.00	60.00	3.00	77	1516	280
		69.8-71.0m; diorite dyke; 1mm felds (finer than diorite porphyry); minor mgt		933366	60.00	63.00	3.00	97	737	74
		71-73m; minor mgt, chl alt		933367	63.00	66.00	3.00	83	981	81
				933368	66.00	69.00	3.00	86	1023	76
				933369	69.00	72.00	3.00	96	2433	175
				933370	72.00	75.00	3.00	97	1869	105
				933371	75.00	78.00	3.00	98	1043	89
				933372	78.00	81.00	3.00	96	684	57
				933373	81.00	84.00	3.00	104	1077	59
				933374	84.00	87.00	3.00	103	1763	92
85.3	97.9	chl-mgt alt volcanic?								
		less broken than above interval	VO	933375	87.00	90.00	3.00	100	1804	112
		gn gm with mgt flooding; poss local felds discernible; local dykes, or is entire interval a very alt int?		933376	90.00	93.00	3.00	102	2356	139
		local strong biot		933377	93.00	96.00	3.00	99	2245	141
		py to 0.5%; tr cp		933378	96.00	99.00	3.00	103	997	81
97.9	100.4	feldspar porphyry	FP	933379	99.00	102.00	3.00	100	607	40

ZY-08-11										
depth (m)		description	litho code	sample #	from	to	length (m)	rec %	Cu	Au
from	to							%	ppm	ppb
		bn-gn gm with scat wh felds, locally to 8mm; chl alt mafics; local rnd lithic frags		933380	102.00	105.00	3.00	94	2168	156
100.4	148.5	buff-bn ser alt siltstone	ST	933381	105.00	108.00	3.00	94	1697	127
		local biot, chl, mgt alt		933382	108.00	111.00	3.00	100	1618	125
		common dk gy-bk frax		933383	111.00	114.00	3.00	101	1880	101
		100.4-104.5m; chl-mgt alt; 5% cp+py diss masses from 102.5-102.7m		933384	114.00	117.00	3.00	104	1504	131
		105-111m; abund 45CA carb vns with local mgt, tr cp		933385	117.00	120.00	3.00	104	3156	198
		108.9-110.9m; gn saus alt around 3x3 0.3?m diorite porphyry dykes		933386	120.00	123.00	3.00	104	2366	142
		114.8-115.5m; feldspar porphyry dyke		933387	123.00	126.00	3.00	98	2319	133
		118-119.5m; dk gn chl-mgt alt volcanic?; diss py to 2%, cp to 0.5%		933388	126.00	129.00	3.00	90	1637	89
		120.5-121.5m; strong biot		933389	129.00	132.00	3.00	103	2122	125
		121.5-124.5m; biot+mgt alt; minor cp, py		933390	Standard CDN-CGS-6					
		124.5-128m; lt gy-gn ser alt; minor biot; py to 0.5%, tr cp		933391	132.00	135.00	3.00	98	1831	176
		128-133.6m; biot alt; local mgt; 0.2% cp in frax; py to 0.5%		933392	135.00	138.00	3.00	98	1674	146
		133.6-135.3m; diorite porphyry dyke; gn gm, wh felds; chill margins		933393	138.00	141.00	3.00	95	1292	75
		136.5-148.5m; v broken; local strong biot		933394	141.00	144.00	3.00	100	710	54
		148.5m; 40CA qv with mo at lower contact		933395	144.00	147.00	3.00	104	265	32
148.5	169.35	lt gy-gn ser-biot alt diorite porphyry	DP	933396	147.00	150.00	3.00	101	818	73
		20-30% wh-lt gn felds to 5mm		933397	150.00	153.00	3.00	98	1143	88
		minor saus alt; strong biot alt to 151m		933398	153.00	156.00	3.00	104	600	38
		biot alt as fine bn flooding, though also local zones with fresh bk fine biots		933399	156.00	159.00	3.00	97	633	40
		1% diss py, tr cp, mo		933400	159.00	162.00	3.00	98	491	47
		154-155m; xenos of fg bn hornfels		933401	162.00	165.00	3.00	102	601	30
				933402	165.00	168.00	3.00	97	393	14
				933403	168.00	171.00	3.00	102	613	35
169.35	180.5	lt bn strongly biot alt int	DK	933404	171.00	174.00	3.00	88	405	25
		mass bn rock with local felds discernible in some sections		933405	174.00	177.00	3.00	120	488	23
		diss py to 1%; tr cp		933406	177.00	180.00	3.00	97	643	28
180.5	259.08	gy ser alt siltstone/fg sandstone	ST	933407	180.00	183.00	3.00	90	382	14
		low-mod CA bedding		933408	183.00	186.00	3.00	96	935	60
		broken; local soft clay alt intervals		933409	186.00	189.00	3.00	96	143	24
		locally abund dark ser-py frax, stwks		933410	189.00	192.00	3.00	101	236	21
		1-2% py overall, locally narrow intervals to 30%; tr cp		933411	192.00	195.00	3.00	100	1429	37
		183-186m; fg py masses to 20%		933412	195.00	198.00	3.00	93	341	17
		192.5-193m; 40% py, tr cp		933413	198.00	201.00	3.00	103	529	15
		215-EOH; local cgl beds		933414	201.00	204.00	3.00	106	134	28
		225.8m; 40cm of mass mgt, 5%py		933415	204.00	207.00	3.00	100	221	27
		228.5-EOH; zones to 1m of 20% py, locally with mgt, biot, chl		933416	207.00	210.00	3.00	83	411	23
		243-252m; fg ss, less broken; py dec to 1%		933417	210.00	213.00	3.00	76	239	22
				933418	213.00	216.00	3.00	57	212	22
		EOH		933419	216.00	219.00	3.00	90	245	19
				933420	Standard CDN-CGS-6					
				933421	219.00	222.00	3.00	113	225	21
				933422	222.00	225.00	3.00	101	298	37
				933423	225.00	228.00	3.00	85	250	27
				933424	228.00	231.00	3.00	83	612	45
				933425	231.00	234.00	3.00	116	212	23
				933426	234.00	237.00	3.00	100	246	38

PROPERTY: ZYMO				Loc Method: GPS		dip tests				
Hole # ZY-08-12				UTM E	562172	depth	corrected dip			
Depth (m); 281.94				UTM N	6077037	no test		Start Date: Sept 17/08		
Core size; NQ				Azimuth: 037°				Completion: Sept 19/08		
Drilled by; Driftwood Diamond Drilling				Inclination: -59°		GRID W	140+00W	Logged By: Johnston		
NOTES;				Elevation: 1318m		GRID N	96+60N	Date Logged; Sept 28-Oct 1/08		
ZY-08-12										
depth (m)		description	litho code	sample #	from	to	length (m)	rec %	Cu ppm	Au ppb
from	to									
0.00	3.05	casing	ST	933435	3.05	6.00	2.95	58	1291	55
				933436	6.00	9.00	3.00	98	1649	73
3.05	23.3	lt gy ser alt siltstone		933437	9.00	12.00	3.00	82	395	27
		v broken; abund wh carbs		933438	12.00	15.00	3.00	118	437	27
		local ep in vns, diss with py		933439	15.00	18.00	3.00	78	373	20
		local 1-2cm wh qv's with py		933440	18.00	21.00	3.00	98	759	40
		8.9-9.5m; gn chl alt diorite dyke; gn chl alt felds to 5mm		933441	21.00	24.00	3.00	101	1501	98
		14.5-17.5m; lt bn biot alt; local in qv's								
		21-22.3m; biot alt cgl; py to 0.5%, minor cp								
23.3	31.1	gn chl-biot alt fg diorite	DK	933442	24.00	27.00	3.00	90	832	45
		gn chl-biot alt gm with wh felds		933443	27.00	30.00	3.00	100	757	37
		wk mgt; diss ep; mgt with ep in local qv's		933444	30.00	33.00	3.00	94	360	11
		py to 0.5%, tr diss cp								
		26.2-27.1m; xenos of bn hornfelses sltn								
31.1	60	hornfelses siltstone/ss	HF	933445	33.00	36.00	3.00	83	441	16
		mod broken		933446	36.00	39.00	3.00	87	336	9
		bn biot alt; local sil'n; local wk-mod mgt; ep as diss, local frax		933447	39.00	42.00	3.00	103	383	15
		1% diss py; tr cp		933448	42.00	45.00	3.00	96	658	20
		32.8-33.4m; fg diorite dyke		933449	45.00	48.00	3.00	106	435	14
		51.5-53m; bleached around abund qtz-ep vns		933450	Standard CDN-CGS-6					
		57-60m; coarsens to ss		933451	48.00	51.00	3.00	96	396	13
		57.5-58.5m; strong bleaching around frax		933452	51.00	54.00	3.00	96	1575	77
				933453	54.00	57.00	3.00	98	1126	82
				933454	57.00	60.00	3.00	90	829	66
60	70	lt gy ser-sil hornfelses ss/conglomerate	ST	933455	60.00	63.00	3.00	104	740	43
		locally magnetic		933456	63.00	66.00	3.00	113	771	35
				933457	66.00	69.00	3.00	82	1026	52
70	88	lt gy ser-sil alt fg tuff?	VO	933458	69.00	72.00	3.00	96	2478	142
		gy gm with fine felds; also subround alt frags		933459	72.00	75.00	3.00	113	1692	105
		variably magnetic; local mgt vns; local wh qv's; minor ep		933460	75.00	78.00	3.00	100	707	36
				933461	78.00	81.00	3.00	99	1204	64
				933462	81.00	84.00	3.00	103	1219	49
				933463	84.00	87.00	3.00	97	1069	38
				933464	87.00	90.00	3.00	92	1158	50
88	116.65	lt gy-bn hornfelses siltstone	ST	933465	90.00	93.00	3.00	95	1112	49
		biot-sil alt; minor mgt, ep		933466	93.00	96.00	3.00	105	965	41
		py to 2%; tr cp		933467	96.00	99.00	3.00	70	2093	93
		90-94m; v broken		933468	99.00	102.00	3.00	108	943	35
		112.5-114m; ss		933469	102.00	105.00	3.00	120	540	23
				933470	105.00	108.00	3.00	98	531	20

ZY-08-12										
depth (m)		description	litho code	sample #	from	to	length (m)	rec %	Cu ppm	Au ppb
from	to									
				933471	108.00	111.00	3.00	93	837	27
				933472	111.00	114.00	3.00	108	1035	50
				933473	114.00	117.00	3.00	94	714	21
116.65	135.85	hornfels with dykes	HF	933474	117.00	120.00	3.00	102	394	19
		lt gy-bn hornfelsed sltn/ss as above intruded by fresh diorite dykes to 1.6m; dykes with felds to 1mm, local unalt hb's; local fresh fine biot (alt?), common ep, py to 1%, local mgt vns		933475	120.00	123.00	3.00	100	977	38
		116-.65-117m; dyke	HF	933476	123.00	126.00	3.00	103	1608	97
		1390.2-130.4m; dyke		933477	126.00	129.00	3.00	97	1571	85
		132.6-132.8m; dyke		933478	129.00	132.00	3.00	97	798	28
		134.12-135.85m; dyke		933479	132.00	135.00	3.00	97	737	23
				933480	Standard CDN-CGS-6					
135.85	154	gy-bn hornfelsed siltstone/fg ss	HF	933481	135.00	138.00	3.00	98	1639	71
		wk-mod sil'n; local bleaching; minor wh qv's		933482	138.00	141.00	3.00	100	594	21
		145.7-155.15m; biot-saus alt feldspar porphyry dykes; to 30cm		933483	141.00	144.00	3.00	99	434	15
				933484	144.00	147.00	3.00	102	688	40
				933485	147.00	150.00	3.00	100	1039	44
				933486	150.00	153.00	3.00	101	527	24
				933487	153.00	156.00	3.00	95	466	34
154	171.85	gy sil'd siltstone	ST	933488	156.00	159.00	3.00	100	339	23
		minor py; weakly calc; 0.5% frax py; tr cp		933489	159.00	162.00	3.00	98	443	26
		167-171.85m; zones with abund wh carb vns		933490	162.00	165.00	3.00	103	199	10
		sharp 60CA bedding contact at bottom		933491	165.00	168.00	3.00	90	158	9
				933492	168.00	171.00	3.00	103	704	40
171.85	255	hornfelsed fg ss	HF	933493	171.00	174.00	3.00	115	290	13
		dk bn biot alt; local sil'n xcut by lt gy-gn bleached zones around frax		933494	174.00	177.00	3.00	90	307	48
		local sil'n; minor ep		933495	177.00	180.00	3.00	93	312	25
		py to 1% in frax, vns; local cp in frax; tr mo		933496	180.00	183.00	3.00	96	340	22
		222.5-224.9m; fg gn-bn biot-chl alt diorite dyke		933497	183.00	186.00	3.00	96	315	17
		243m; biot alt dec		933498	186.00	189.00	3.00	111	134	6
		253.0-254.5m; lt gy-bn ser-biot alt fg diorite		933499	189.00	192.00	3.00	97	279	18
				933500	192.00	195.00	3.00	97	604	34
				933501	195.00	198.00	3.00	99	436	26
				933502	198.00	201.00	3.00	92	264	14
				933503	201.00	204.00	3.00	97	317	20
				933504	204.00	207.00	3.00	102	451	27
				933505	207.00	210.00	3.00	99	193	16
				933506	210.00	213.00	3.00	97	340	25
				933507	213.00	216.00	3.00	95	276	26
				933508	216.00	219.00	3.00	94	311	18
				933509	219.00	222.00	3.00	100	982	114
				933510	Standard CDN-CGS-6					
				933511	222.00	225.00	3.00	98	362	22
				933512	225.00	228.00	3.00	101	741	35
				933513	228.00	231.00	3.00	100	190	16
				933514	231.00	234.00	3.00	103	255	21
				933515	234.00	237.00	3.00	70	212	16



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.

Vancouver BC V6C 1Z7 Canada

Submitted By:

Glen Garratt

Receiving Lab:

Canada-Smithers

Received:

July 04, 2008

Report Date:

July 21, 2008

Page:

1 of 3

CERTIFICATE OF ANALYSIS

SMI08000582.1

CLIENT JOB INFORMATION

Project: Zymo
Shipment ID: zy-rk-08-01
P.O. Number
Number of Samples: 47

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
DISP-RJT Dispose of Reject After 90 days

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Mincord Exploration Consultants Ltd.
110 - 325 Howe St.
Vancouver BC V6C 1Z7
Canada

CC: Bob Johnston

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status
R150	47	Crush, split and pulverize rock to 200 mesh		
1DX15	47	1:1:1 Aqua Regia digestion ICP-MS analysis	15	Completed

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only. All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.



AcmeLabs ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
Report Date: July 21, 2008

Page: 2 of 3 **Part** 1

CERTIFICATE OF ANALYSIS

SMI08000582.1

Method	Analyte	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca
Unit	MDL	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%
		0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01
140009	Rock	1.61	1.1	4.7	27.7	<1	0.4	3.5	0.4	54	1.81	15.6	<0.1	28.7	0.6	10	<0.1	0.5	3.0	8	<0.01
140010	Rock	2.10	1.2	83.4	28.8	145	0.5	10.6	11.3	2766	2.85	40.1	5.2	10.8	6.2	36	0.8	6.6	1.4	20	0.73
140011	Rock	1.98	4.2	20.7	5.6	71	<0.1	8.9	12.4	967	4.35	25.0	0.1	<0.5	0.9	18	0.1	0.3	<0.1	65	0.75
140012	Rock	1.61	2.9	19.5	118.2	42	1.7	3.7	2.4	81	3.96	49.1	2.4	90.5	4.6	16	<0.1	0.3	6.1	9	0.03
140013	Rock	1.90	1.5	29.1	25.4	241	0.2	5.1	9.2	1190	2.77	15.3	3.0	3.1	5.7	179	1.1	0.1	0.7	40	2.81
140014	Rock	2.02	1.8	29.1	10.3	81	0.1	14.6	23.6	1241	3.64	23.9	1.4	1.2	3.3	96	0.4	0.2	0.1	76	4.75
140015	Rock	2.05	1.7	89.7	68.8	406	0.6	6.4	13.9	1877	3.70	44.8	4.0	6.1	5.9	52	0.9	0.3	0.2	55	1.92
140016	Rock	2.43	0.9	30.3	13.4	75	<0.1	3.1	10.6	1233	2.77	11.4	2.4	1.0	4.7	110	0.5	0.1	<0.1	60	3.82
140017	Rock	2.56	4.1	21.8	102.5	232	1.1	3.4	8.2	8021	2.74	48.2	5.0	6.6	6.0	79	1.1	0.4	<0.1	25	3.84
140018	Rock	2.57	1.0	23.8	10.3	201	0.2	44.6	9.1	1455	3.00	7.2	1.5	2.2	2.0	51	0.5	0.2	0.2	49	0.24
140019	Rock	2.10	0.6	25.3	3.3	50	<0.1	6.7	10.3	849	2.94	3.2	1.9	0.7	4.0	43	<0.1	<0.1	<0.1	89	0.63
140020	Rock	1.80	0.8	110.2	20.9	81	0.2	6.1	16.6	1038	3.51	3.8	2.6	<0.5	7.1	33	1.2	<0.1	<0.1	91	0.74
140021	Rock	1.96	0.5	27.4	8.5	68	<0.1	5.0	11.1	1469	3.25	4.0	4.1	0.5	8.8	113	0.2	0.2	<0.1	101	2.25
140022	Rock	2.21	1.4	51.5	24.9	125	0.4	17.2	11.2	604	4.56	32.2	0.2	10.8	0.8	24	0.4	2.3	0.7	28	1.37
140023	Rock	2.22	1.2	23.4	42.6	105	0.3	6.1	8.8	681	3.87	16.9	0.1	1.8	0.5	22	0.8	0.6	0.4	29	0.51
140024	Rock	2.20	1.9	43.5	5.9	20	<0.1	2.5	3.1	277	0.62	54.2	5.3	6.2	7.3	12	<0.1	6.5	0.3	5	0.28
140025	Rock	1.79	2.6	9.9	104.2	197	0.1	9.4	5.7	1288	2.06	47.5	7.5	1.3	9.4	59	0.9	0.3	0.2	12	1.30
140026	Rock	2.29	1.7	28.2	19.7	319	0.3	9.5	7.0	1106	2.52	9.5	<0.1	1.5	0.5	48	1.8	0.9	0.1	19	1.51
140027	Rock	2.18	3.7	67.2	64.8	294	1.1	7.1	8.4	1163	3.46	20.8	0.3	2.7	0.7	73	2.0	1.1	6.9	25	2.15
140028	Rock	2.01	1.7	10.8	52.9	19	1.1	1.7	0.6	132	1.82	23.8	<0.1	3.0	0.8	8	<0.1	8.6	1.7	8	0.02
140029	Rock	1.75	1.8	15.3	310.5	470	0.7	3.6	5.1	2900	1.84	50.2	5.5	14.5	9.7	40	1.8	3.1	0.6	5	1.75
140030	Rock	0.87	1.6	34.6	741.3	730	0.4	5.4	7.7	2180	2.31	15.8	2.9	10.5	7.4	97	4.3	0.9	0.2	18	2.44
140031	Rock	1.90	0.9	108.7	34.2	298	1.8	5.1	11.3	516	6.54	139.3	<0.1	7.9	0.3	6	1.1	3.6	6.9	50	0.07
140032	Rock	1.83	1.6	36.2	96.8	158	0.7	1.8	1.7	177	4.48	109.9	0.1	8.3	0.7	4	0.1	1.7	3.0	14	0.05
140033	Rock	1.97	1.1	4.7	12.7	36	0.1	13.1	3.6	89	3.36	15.6	0.1	5.6	0.3	11	<0.1	0.3	0.8	5	0.02
140034	Rock	1.70	1.0	6.3	30.9	127	<0.1	4.4	4.9	1602	2.81	19.5	2.7	5.5	8.1	13	0.4	0.3	0.8	22	0.60
140035	Rock	2.03	0.4	4.4	5.8	19	<0.1	12.8	1.6	98	2.10	37.8	0.2	10.4	1.9	10	<0.1	0.2	2.1	15	0.01
140036	Rock	2.14	0.8	6.7	4.8	17	<0.1	25.1	13.2	61	4.31	13.0	0.1	4.6	1.4	7	<0.1	0.2	3.1	12	0.04
140037	Rock	1.78	2.9	21.0	3.5	25	<0.1	42.1	14.4	166	3.15	31.9	0.3	42.9	3.2	9	<0.1	0.4	3.4	18	0.03
140038	Rock	1.73	0.9	7.7	18.7	90	0.1	4.5	5.2	1194	2.45	28.2	4.6	3.2	10.1	40	0.3	0.2	1.5	18	1.19

This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
 Report Date: July 21, 2008

Page: 2 of 3 Part 2

CERTIFICATE OF ANALYSIS

SMI08000582.1

Method	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se	
Unit	%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
MDL	0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.01	0.01	0.1	0.01	0.05	1	0.5	
140009	Rock	0.033	9	12	0.03	185	<0.001	1	0.28	0.009	0.28	<0.1	0.03	0.6	0.2	0.30	<1	1.0
140010	Rock	0.127	17	5	0.14	58	<0.001	7	0.74	0.019	0.36	0.2	0.03	2.7	0.5	1.03	2	<0.5
140011	Rock	0.081	9	14	0.16	209	0.001	3	0.91	0.022	0.13	<0.1	0.15	9.2	<0.1	<0.05	2	<0.5
140012	Rock	0.083	7	4	0.04	63	0.001	3	0.50	0.009	0.32	<0.1	0.04	1.0	0.4	1.19	2	6.2
140013	Rock	0.142	16	5	0.79	56	0.001	3	0.69	0.032	0.29	<0.1	0.05	3.7	0.3	1.10	2	<0.5
140014	Rock	0.178	25	15	1.53	385	0.005	12	1.16	0.026	0.32	<0.1	0.06	8.6	0.5	0.33	3	<0.5
140015	Rock	0.158	23	4	0.40	189	<0.001	7	0.92	0.027	0.29	<0.1	0.04	5.9	0.7	0.34	2	0.6
140016	Rock	0.185	27	3	1.04	905	0.001	10	1.11	0.014	0.41	<0.1	0.01	5.0	0.7	0.14	3	<0.5
140017	Rock	0.142	26	2	1.11	77	<0.001	5	0.94	0.011	0.42	<0.1	0.11	5.5	1.8	1.10	2	<0.5
140018	Rock	0.060	11	33	0.10	1725	0.001	6	1.07	0.006	0.45	<0.1	0.03	6.4	1.4	<0.05	3	<0.5
140019	Rock	0.158	16	10	0.30	190	0.072	6	1.29	0.074	0.25	<0.1	<0.01	7.9	<0.1	<0.05	5	<0.5
140020	Rock	0.168	24	5	0.05	125	0.002	7	1.06	0.029	0.28	<0.1	<0.01	6.0	0.2	<0.05	3	<0.5
140021	Rock	0.195	31	7	0.84	556	0.037	5	0.97	0.069	0.19	<0.1	<0.01	7.5	0.2	<0.05	8	<0.5
140022	Rock	0.030	6	14	0.56	31	0.002	2	1.34	0.028	0.26	<0.1	0.05	4.4	0.2	1.87	4	2.1
140023	Rock	0.046	13	6	0.91	178	0.001	2	1.91	0.028	0.32	<0.1	0.02	5.6	0.2	0.46	5	0.7
140024	Rock	0.079	15	3	0.04	185	<0.001	3	0.59	0.019	0.28	0.1	0.17	1.2	0.2	<0.05	1	<0.5
140025	Rock	0.088	20	5	0.23	429	<0.001	6	0.73	0.054	0.30	<0.1	0.05	1.8	0.2	0.25	2	<0.5
140026	Rock	0.068	4	6	0.30	71	<0.001	2	0.39	0.040	0.18	<0.1	0.06	3.2	0.1	0.66	<1	1.1
140027	Rock	0.064	5	3	0.36	87	<0.001	2	0.64	0.024	0.28	0.1	0.09	6.0	0.3	1.32	1	0.7
140028	Rock	0.029	7	3	0.02	98	<0.001	2	0.50	0.013	0.32	0.1	0.11	2.1	0.4	0.09	1	<0.5
140029	Rock	0.074	8	2	0.29	164	<0.001	2	0.38	0.012	0.23	0.1	0.32	1.1	0.4	0.51	1	<0.5
140030	Rock	0.095	15	2	0.29	161	0.001	2	0.43	0.022	0.22	<0.1	0.34	1.9	0.2	0.36	1	<0.5
140031	Rock	0.028	4	5	0.12	98	<0.001	2	1.06	0.013	0.21	0.1	0.08	4.2	0.5	1.02	2	1.6
140032	Rock	0.053	5	3	0.01	60	<0.001	2	0.44	0.008	0.24	0.1	0.09	1.8	0.5	0.33	1	<0.5
140033	Rock	0.015	<1	9	0.01	48	<0.001	3	0.33	0.007	0.21	0.1	0.01	0.9	0.3	1.77	<1	1.1
140034	Rock	0.111	21	3	0.18	174	0.002	3	0.63	0.020	0.29	<0.1	<0.01	2.2	0.4	0.91	2	<0.5
140035	Rock	0.026	9	14	0.02	100	<0.001	2	0.59	0.030	0.29	<0.1	0.03	1.2	0.3	0.16	1	<0.5
140036	Rock	0.063	4	17	0.01	40	<0.001	1	0.38	0.033	0.14	<0.1	0.04	1.1	0.2	2.81	1	2.3
140037	Rock	0.033	22	20	0.06	113	<0.001	2	0.62	0.018	0.25	<0.1	0.03	1.7	0.3	0.66	1	0.7
140038	Rock	0.101	13	4	0.40	95	0.001	2	0.51	0.038	0.20	<0.1	0.03	2.0	0.3	1.56	1	<0.5

This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
 Report Date: July 21, 2008

Page: 3 of 3 Part 1

CERTIFICATE OF ANALYSIS

SMI08000582.1

Method	Analyte	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca
Unit	Unit	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	ppm	
MDL	MDL	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	0.1	2	0.01
140039	Rock	1.96	1.3	314.2	8.6	26	2.1	15.4	2.4	228	3.58	12.6	0.2	13.4	0.6	11	<0.1	0.5	3.9	18	0.01
140040	Rock	2.43	2.6	12.7	96.1	639	0.5	4.8	6.4	1702	3.79	10.5	5.0	2.1	10.6	42	2.6	0.3	1.6	57	0.67
140041	Rock	1.86	1.2	191.2	125.5	390	2.4	6.6	2.3	113	4.12	20.0	3.5	19.3	11.2	26	0.5	0.1	79.2	35	0.14
140042	Rock	2.84	5.1	2.8	20.0	2	0.1	3.2	0.4	34	0.92	1.6	0.1	5.7	0.6	6	<0.1	0.2	0.9	5	<0.01
140043	Rock	2.41	11.0	3.7	27.0	22	0.4	6.5	1.1	36	1.67	4.8	0.2	5.6	0.7	11	<0.1	0.4	1.0	8	<0.01
140044	Rock	1.91	2.3	11.1	21.3	174	0.1	5.8	10.2	1316	3.51	498.2	1.6	<0.5	3.3	47	0.3	7.3	0.4	67	0.08
140045	Rock	1.65	1.4	8.1	17.3	27	0.6	4.7	11.2	119	4.34	58.4	3.7	37.2	6.6	20	<0.1	0.2	7.0	15	0.21
140046	Rock	1.84	2.5	45.6	2548	318	1.3	1.3	0.8	418	2.29	70.8	3.8	76.7	9.9	36	0.6	0.7	0.8	11	0.07
140047	Rock	1.86	8.6	208.8	5.9	73	0.1	5.8	9.9	527	3.19	4.5	2.1	7.9	5.4	39	0.2	<0.1	0.5	55	0.20
140048	Rock	1.63	3.2	15.5	27.7	72	0.1	3.9	7.6	265	3.62	11.3	3.7	5.6	8.1	16	0.4	<0.1	0.9	20	0.37
140049	Rock	2.19	1.6	13.9	151.4	35	0.5	1.7	1.3	132	3.16	36.2	2.7	5.1	6.3	15	<0.1	0.2	2.8	20	0.04
140050	Rock	2.25	2.8	78.0	28.8	37	0.2	1.8	1.2	50	3.20	3.8	2.2	3.4	5.6	17	<0.1	0.1	3.1	16	0.02
726501	Rock	1.94	3.6	18.0	4.3	34	0.3	20.4	1.7	125	1.76	82.9	0.3	2.4	5.0	16	<0.1	0.9	0.2	22	0.01
726502	Rock	2.06	2.6	8.0	16.1	126	<0.1	5.1	9.0	1889	2.78	0.9	5.2	<0.5	10.7	117	0.4	0.3	<0.1	55	1.49
726503	Rock	1.85	2.4	20.7	29.6	148	0.1	4.3	9.7	2052	3.19	19.0	4.2	2.1	7.3	137	0.3	0.3	0.2	56	1.39
726504	Rock	2.18	0.9	44.7	8.2	90	0.3	10.9	8.7	1570	2.79	4.7	3.2	0.8	7.1	98	0.2	0.6	<0.1	46	1.89
726505	Rock	2.01	1.8	8.9	118.8	463	0.3	3.8	4.1	1116	2.54	4.6	1.7	9.4	10.3	28	1.5	0.1	1.6	46	0.46



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
Report Date: July 21, 2008

Page: 3 of 3 **Part** 2

CERTIFICATE OF ANALYSIS

SMI08000582.1

Method	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se	
Unit	%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
MDL	0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5	
140039	Rock	0.029	6	14	0.01	61	<0.001	1	0.22	0.005	0.22	<0.1	0.02	1.3	0.2	0.48	<1	2.3
140040	Rock	0.156	36	6	0.53	341	0.005	4	1.47	0.044	0.31	<0.1	0.08	3.2	0.3	0.18	6	<0.5
140041	Rock	0.144	39	7	0.04	159	<0.001	2	0.66	0.031	0.30	<0.1	0.13	2.4	0.3	0.54	2	2.4
140042	Rock	0.008	6	9	0.01	90	<0.001	2	0.26	0.009	0.23	<0.1	0.03	0.6	0.2	0.22	<1	<0.5
140043	Rock	0.008	6	13	0.01	352	0.001	2	0.44	0.019	0.34	<0.1	0.03	0.8	0.3	0.27	1	2.2
140044	Rock	0.072	8	8	0.05	110	0.001	8	0.92	0.046	0.07	<0.1	0.02	5.4	1.9	<0.05	3	<0.5
140045	Rock	0.152	7	4	0.07	22	0.002	2	0.80	0.008	0.42	<0.1	0.08	1.9	0.7	3.84	2	4.9
140046	Rock	0.104	18	3	0.02	433	<0.001	2	0.55	0.005	0.42	0.1	0.13	1.3	0.6	0.32	1	<0.5
140047	Rock	0.120	12	4	0.05	501	0.001	3	0.86	0.042	0.29	<0.1	<0.01	7.3	0.4	0.19	2	1.6
140048	Rock	0.148	24	3	0.13	70	0.001	3	0.92	0.015	0.37	<0.1	<0.01	2.5	0.6	1.94	2	3.7
140049	Rock	0.151	4	3	0.09	196	0.002	2	0.89	0.011	0.47	<0.1	0.01	1.8	0.6	0.22	3	1.6
140050	Rock	0.106	7	3	0.05	362	0.001	2	0.77	0.012	0.28	<0.1	<0.01	1.0	0.3	0.35	2	1.8
726501	Rock	0.029	23	12	0.03	86	<0.001	1	0.71	0.023	0.33	<0.1	<0.01	1.9	0.4	<0.05	2	<0.5
726502	Rock	0.153	34	6	0.36	686	0.004	3	0.93	0.030	0.27	<0.1	<0.01	3.5	0.5	<0.05	4	<0.5
726503	Rock	0.144	26	4	0.44	444	0.002	5	0.95	0.047	0.25	<0.1	<0.01	3.9	0.3	0.33	5	<0.5
726504	Rock	0.127	23	8	0.38	401	0.002	5	1.14	0.030	0.31	<0.1	<0.01	5.0	0.3	0.31	4	<0.5
726505	Rock	0.158	25	4	0.17	201	0.001	3	0.90	0.029	0.28	<0.1	<0.01	3.8	0.4	0.52	3	<0.5

QUALITY CONTROL REPORT

SMI08000582.1

Method	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
Unit	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	
MDL	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	
Pulp Duplicates																					
140041	Rock	1.86	1.2	191.2	125.5	390	2.4	6.6	2.3	113	4.12	20.0	3.5	19.3	11.2	26	0.5	0.1	79.2	35	0.14
REP 140041	QC		1.3	193.8	128.8	393	2.4	7.6	2.4	119	4.28	21.0	3.9	21.1	11.2	27	0.5	0.1	82.6	38	0.15
Reference Materials																					
STD DS7	Standard		21.1	104.8	68.7	389	0.8	56.3	10.0	633	2.39	49.9	5.0	58.8	4.7	73	6.2	5.9	4.3	86	1.01
STD DS7	Standard		20.8	110.3	68.8	398	0.9	57.3	9.8	658	2.44	51.2	5.1	59.3	4.8	76	6.1	5.8	4.4	91	1.05
STD DS7	Standard		19.3	121.2	72.1	423	0.8	56.7	10.4	657	2.54	55.7	5.4	69.4	5.0	81	6.8	5.5	4.8	87	1.03
STD DS7	Standard		22.0	119.1	73.4	426	0.9	57.6	10.8	659	2.58	56.1	5.7	77.8	5.2	89	6.8	6.1	5.0	90	1.10
STD DS7 Expected			20.92	109	70.6	411	0.89	56	9.7	627	2.39	48.2	4.9	70	4.4	68.7	6.38	5.86	4.51	86	0.93
BLK	Blank		<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01
BLK	Blank		<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01
Prep Wash																					
G1	Prep Blank	<0.01	0.9	2.9	3.5	51	<0.1	6.8	4.9	624	2.05	<0.5	3.1	0.8	5.4	79	<0.1	<0.1	<0.1	43	0.63
G1	Prep Blank	<0.01	0.7	2.7	3.3	46	<0.1	5.9	4.5	564	2.00	<0.5	2.8	1.1	5.0	76	<0.1	<0.1	<0.1	40	0.63

QUALITY CONTROL REPORT

SMI08000582.1

Method		1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte		P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
Unit		%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm
MDL		0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5
Pulp Duplicates																		
140041	Rock	0.144	39	7	0.04	159	<0.001	2	0.66	0.031	0.30	<0.1	0.13	2.4	0.3	0.54	2	2.4
REP 140041	QC	0.145	38	7	0.04	162	0.001	1	0.64	0.031	0.32	<0.1	0.13	2.7	0.3	0.56	2	2.6
Reference Materials																		
STD DS7	Standard	0.072	14	197	1.03	370	0.125	38	1.05	0.091	0.45	3.8	0.20	2.4	4.1	0.19	5	3.0
STD DS7	Standard	0.073	15	215	1.07	380	0.128	41	1.11	0.095	0.46	3.8	0.20	2.7	4.2	0.19	5	3.4
STD DS7	Standard	0.085	15	208	1.11	340	0.131	38	1.11	0.094	0.47	3.4	0.23	2.8	4.5	0.20	5	3.4
STD DS7	Standard	0.087	16	210	1.14	385	0.143	44	1.18	0.108	0.47	3.9	0.25	3.0	4.6	0.20	6	3.7
STD DS7 Expected		0.08	12.7	163	1.05	370.3	0.124	38.6	0.959	0.073	0.44	3.8	0.2	2.5	4.19	0.21	4.6	3.5
BLK	Blank	<0.001	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
BLK	Blank	<0.001	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
Prep Wash																		
G1	Prep Blank	0.083	12	15	0.62	227	0.156	<1	1.19	0.098	0.55	0.2	<0.01	2.5	0.4	<0.05	6	<0.5
G1	Prep Blank	0.078	12	16	0.58	206	0.141	1	1.14	0.091	0.48	<0.1	<0.01	2.3	0.4	<0.05	6	<0.5



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.

Vancouver BC V6C 1Z7 Canada

Submitted By:

Glen Garratt

Receiving Lab:

Canada-Smithers

Received:

July 07, 2008

Report Date:

July 23, 2008

Page:

1 of 3

CERTIFICATE OF ANALYSIS

SMI08000590.1

CLIENT JOB INFORMATION

Project: Zymo
Shipment ID: zy-rk-08-02
P.O. Number
Number of Samples: 31

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
DISP-RJT Dispose of Reject After 90 days

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Mincord Exploration Consultants Ltd.
110 - 325 Howe St.
Vancouver BC V6C 1Z7
Canada

CC: Bob Johnston

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status
R150	31	Crush, split and pulverize rock to 200 mesh		
1DX15	31	1:1:1 Aqua Regia digestion ICP-MS analysis	15	Completed

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only. All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**

110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo

Report Date: July 23, 2008

Page: 2 of 3 Part 1

CERTIFICATE OF ANALYSIS

SMI08000590.1

Method	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
Unit	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	
MDL	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	
726506	Rock	1.45	4.7	73.0	46.2	116	0.4	6.3	21.1	957	5.68	7.1	6.3	23.9	6.4	56	0.6	0.2	3.0	34	1.97
726507	Rock	1.80	15.2	539.6	52.5	64	0.5	5.5	23.9	419	4.42	12.5	4.7	24.7	3.9	30	0.3	0.3	2.6	19	1.08
726508	Rock	2.16	2.3	83.6	91.3	51	1.4	3.2	5.4	458	3.72	42.5	4.0	25.0	7.5	11	0.2	3.4	8.0	7	0.25
726509	Rock	2.38	1.6	206.7	233.0	142	2.3	2.5	5.4	3473	3.35	83.0	3.3	22.8	7.1	13	1.2	10.9	5.3	6	0.67
726510	Rock	1.88	3.0	106.7	61.9	31	1.0	3.1	4.2	76	3.25	52.2	3.3	18.1	7.2	8	<0.1	2.3	2.4	9	0.09
726511	Rock	1.80	1.7	301.4	23.2	34	0.2	3.7	8.7	678	3.58	21.9	8.4	10.0	8.9	18	0.9	0.2	1.5	6	1.09
726512	Rock	3.28	71.8	9994	8994	>10000	>100	2.7	1.4	1478	11.83	7432	8.6	2219	2.4	44	99.3	251.4	41.4	4	0.03
726513	Rock	2.61	1.5	1192	1291	1277	7.6	4.3	6.7	500	3.02	341.1	6.6	22.7	10.0	25	7.7	6.7	13.9	7	0.55
726514	Rock	1.70	5.8	94.0	220.2	68	0.8	3.0	0.5	264	1.98	22.9	1.6	22.9	7.1	16	0.3	1.1	0.7	35	0.10
726515	Rock	2.73	15.7	881.4	290.6	630	1.5	4.9	13.2	602	3.25	15.8	6.6	39.4	9.3	27	4.1	0.2	2.4	17	0.96
726516	Rock	2.20	12.1	747.9	164.0	220	2.5	4.3	27.7	8994	19.81	90.0	12.7	31.7	5.8	124	1.8	0.9	2.1	10	0.75
726517	Rock	2.48	31.0	581.7	34.3	170	1.1	4.2	7.4	908	3.77	38.6	4.4	44.3	10.5	17	0.8	0.4	3.3	36	0.33
726518	Rock	2.39	17.8	182.5	71.4	113	0.7	2.1	2.6	649	3.31	8.8	3.1	96.5	11.5	18	0.1	0.4	1.6	33	0.20
726519	Rock	2.26	13.6	896.0	39.8	194	1.0	4.5	5.9	446	2.69	6.7	5.0	246.1	10.9	15	0.6	0.5	1.4	28	0.28
726520	Rock	2.46	12.7	232.6	13.8	51	0.9	2.3	3.7	193	3.88	3.9	2.9	65.6	11.4	20	<0.1	0.1	1.6	28	0.13
726521	Rock	2.88	14.8	401.2	49.6	129	2.0	2.4	5.0	467	4.68	10.3	2.9	92.2	9.1	29	0.2	0.3	3.4	24	0.08
726522	Rock	2.72	16.7	256.0	30.0	57	1.4	2.1	2.5	404	3.80	7.2	3.7	141.7	10.8	20	<0.1	0.2	7.9	31	0.13
726523	Rock	2.29	2.3	288.6	18.3	58	0.7	2.8	5.6	117	3.95	5.4	4.4	76.2	12.5	13	<0.1	0.2	6.6	15	0.13
726524	Rock	2.12	0.8	55.6	7.0	361	<0.1	16.8	19.8	979	4.67	24.0	0.2	<0.5	0.9	47	2.1	1.0	0.1	94	0.91
726525	Rock	2.03	1.0	59.6	7.6	101	<0.1	7.1	9.6	563	2.93	9.5	3.7	<0.5	4.0	66	0.5	0.6	0.1	60	1.00
726526	Rock	2.53	7.2	37.7	15.3	10	0.1	0.9	0.5	39	35.06	234.9	3.1	6.2	0.8	4	<0.1	25.0	0.3	44	0.01
726527	Rock	2.47	19.0	378.0	62.6	65	1.1	1.9	4.0	38	3.24	32.3	3.5	46.7	8.9	10	0.1	3.7	3.4	10	0.06
726528	Rock	2.12	2.0	32.5	63.2	42	0.8	2.1	1.5	55	2.90	47.8	2.7	29.2	6.7	22	<0.1	7.9	7.0	6	0.05
726529	Rock	2.89	5.7	586.9	45.8	175	0.7	7.1	45.8	4246	8.77	378.6	14.4	22.2	9.3	25	1.0	1.2	4.3	12	0.12
726530	Rock	2.19	5.6	42.3	17.5	10	2.0	4.4	5.8	43	3.25	85.9	1.6	344.7	2.9	9	<0.1	37.1	5.3	5	<0.01
830851	Rock	0.49	2.7	7.6	160.9	110	0.3	3.8	0.5	84	1.33	11.3	0.2	25.9	0.8	7	0.4	1.3	0.8	4	0.03
830852	Rock	2.23	1.3	13.1	8.6	45	<0.1	27.4	11.2	790	2.93	26.9	0.2	2.4	1.0	73	0.2	0.7	0.6	29	2.26
830853	Rock	1.07	1.3	17.1	4.0	35	<0.1	36.0	7.7	410	2.13	19.5	0.2	4.8	0.8	39	0.1	0.6	<0.1	32	1.75
830854	Rock	1.09	1.7	9.3	5.4	63	<0.1	36.2	10.8	345	2.04	18.7	1.3	<0.5	0.8	21	0.2	0.4	<0.1	23	0.67
830855	Rock	1.37	0.5	6.5	3.3	60	<0.1	9.3	10.6	1038	3.23	4.5	0.5	0.9	2.0	72	0.2	0.3	0.1	75	2.80



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**

110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo

Report Date: July 23, 2008

Page: 2 of 3 Part 2

CERTIFICATE OF ANALYSIS

SMI08000590.1

Method	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se	
Unit	%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
MDL	0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5	
726506	Rock	0.156	11	4	0.28	17	0.002	3	0.40	0.028	0.22	<0.1	<0.01	3.1	0.3	4.93	1	4.6
726507	Rock	0.125	4	3	0.23	25	<0.001	4	0.51	0.029	0.24	<0.1	<0.01	2.5	0.4	3.97	1	12.1
726508	Rock	0.117	16	3	0.07	46	<0.001	2	0.34	0.006	0.21	0.1	0.01	0.8	0.5	3.09	<1	4.1
726509	Rock	0.119	14	2	0.16	74	<0.001	1	0.37	0.004	0.24	<0.1	0.02	0.9	0.5	2.03	<1	4.9
726510	Rock	0.158	21	2	0.05	95	0.002	2	0.39	0.006	0.28	0.1	<0.01	0.8	0.5	1.66	<1	7.5
726511	Rock	0.124	8	2	0.47	40	<0.001	1	0.58	0.011	0.22	<0.1	<0.01	1.0	0.5	3.74	1	3.8
726512	Rock	0.024	4	6	<0.01	5	<0.001	<1	0.13	0.003	0.08	5.4	2.57	0.4	2.8	>10	25	25.6
726513	Rock	0.125	18	3	0.17	42	0.001	1	0.57	0.009	0.29	0.2	0.14	0.9	0.7	3.19	2	2.6
726514	Rock	0.104	6	6	0.74	116	0.003	1	1.28	0.058	0.39	<0.1	0.01	1.7	0.7	0.08	4	2.4
726515	Rock	0.150	10	3	0.48	77	0.004	1	1.16	0.030	0.47	0.2	0.02	2.0	0.8	2.93	3	4.4
726516	Rock	0.085	12	<1	0.10	92	0.002	1	3.17	0.008	0.10	0.9	0.05	2.2	0.3	0.51	1	3.1
726517	Rock	0.161	13	4	1.03	79	0.007	1	1.79	0.056	0.37	0.2	0.01	2.9	0.6	1.69	6	2.2
726518	Rock	0.147	6	4	0.70	376	0.005	1	1.52	0.035	0.34	<0.1	<0.01	2.3	0.6	0.14	5	2.1
726519	Rock	0.145	11	4	0.82	102	0.006	1	1.66	0.061	0.39	<0.1	0.09	2.0	0.6	1.66	4	3.3
726520	Rock	0.143	4	3	0.36	232	0.004	1	1.33	0.047	0.44	0.1	<0.01	2.6	0.6	0.59	4	4.0
726521	Rock	0.142	16	5	0.50	46	0.002	1	0.94	0.033	0.29	<0.1	<0.01	1.4	0.4	1.53	4	4.8
726522	Rock	0.132	9	6	0.59	302	0.003	1	1.14	0.041	0.30	0.1	0.02	1.7	0.4	0.52	5	3.9
726523	Rock	0.157	34	2	0.03	77	0.001	<1	0.44	0.012	0.23	<0.1	0.09	1.5	0.3	2.11	1	1.9
726524	Rock	0.067	4	13	0.69	62	<0.001	3	0.71	0.006	0.08	<0.1	0.38	9.4	0.1	<0.05	2	<0.5
726525	Rock	0.144	16	6	0.58	506	0.025	1	1.02	0.061	0.19	0.1	<0.01	6.6	0.2	<0.05	3	<0.5
726526	Rock	1.206	<1	<1	0.02	22	0.009	1	0.18	0.002	0.04	0.2	0.03	0.5	<0.1	2.16	<1	2.0
726527	Rock	0.111	21	2	0.11	134	0.002	1	0.66	0.015	0.32	0.2	0.02	0.9	0.4	0.91	2	4.4
726528	Rock	0.085	4	3	0.03	158	0.001	5	0.32	0.010	0.27	0.5	0.02	0.4	0.3	0.86	<1	3.1
726529	Rock	0.219	27	2	0.05	364	0.002	2	1.41	0.016	0.21	1.6	0.08	3.6	0.5	0.24	2	1.8
726530	Rock	0.026	7	7	0.02	40	0.001	<1	0.30	0.011	0.22	0.5	0.20	0.3	0.2	2.77	<1	2.9
830851	Rock	0.021	14	8	0.01	171	<0.001	2	0.19	0.005	0.13	0.1	<0.01	1.0	0.2	<0.05	<1	2.1
830852	Rock	0.032	4	16	0.44	174	<0.001	2	0.30	0.011	0.11	<0.1	0.03	3.5	<0.1	0.25	<1	0.7
830853	Rock	0.029	2	20	0.36	95	<0.001	2	0.23	0.007	0.08	<0.1	0.03	3.2	<0.1	0.06	<1	<0.5
830854	Rock	0.034	<1	14	0.29	97	<0.001	3	0.33	0.009	0.10	<0.1	0.03	2.9	0.1	0.08	<1	<0.5
830855	Rock	0.148	12	11	0.97	118	0.004	5	0.73	0.026	0.10	0.1	0.01	7.8	<0.1	<0.05	2	<0.5

This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.

Vancouver BC V6C 1Z7 Canada

Project:

Zymo

Report Date:

July 23, 2008

Page:

3 of 3

Part 1

CERTIFICATE OF ANALYSIS

SMI08000590.1

Method	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
Unit	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	
MDL	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	
830856	Rock	1.04	0.5	47.3	743.7	1521	0.8	43.6	14.2	5695	3.53	24.6	0.2	12.7	1.0	19	8.5	0.7	<0.1	38	1.09



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**

110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo

Report Date: July 23, 2008

Page: 3 of 3 Part 2

CERTIFICATE OF ANALYSIS

SMI08000590.1

Method	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
Analyte	P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se	
Unit	%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
MDL	0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5	
830856	Rock	0.042	6	28	0.32	188	<0.001	3	0.40	0.004	0.09	<0.1	0.03	3.8	0.2	0.12	1	<0.5

QUALITY CONTROL REPORT

SMI08000590.1

Method	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
Unit	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	
MDL	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	
Pulp Duplicates																					
REP G1	QC	1.3	2.4	2.9	44	<0.1	4.5	4.1	527	1.76	0.5	2.4	<0.5	4.3	57	<0.1	<0.1	<0.1	34	0.45	
Reference Materials																					
STD DS7	Standard	20.0	115.3	75.0	391	0.8	53.5	9.1	591	2.37	48.2	5.1	112.6	4.6	70	6.7	6.8	5.0	87	0.93	
STD DS7	Standard	20.7	114.4	75.4	394	0.8	54.5	9.2	620	2.38	49.2	5.3	72.7	4.7	72	6.7	6.8	4.9	84	0.96	
STD DS7	Standard	17.7	112.0	64.4	396	0.8	52.8	9.3	596	2.30	49.7	4.5	65.5	3.8	59	5.9	5.8	4.3	83	0.86	
STD DS7	Standard	20.6	111.7	66.4	396	0.8	57.2	9.9	616	2.33	52.5	4.6	63.0	4.0	66	6.0	5.7	4.3	87	0.93	
STD DS7 Expected		20.92	109	70.6	411	0.89	56	9.7	627	2.39	48.2	4.9	70	4.4	68.7	6.38	5.86	4.51	86	0.93	
BLK	Blank	<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01	
BLK	Blank	<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01	
Prep Wash																					
G1	Prep Blank	<0.01																			
G1	Prep Blank	<0.01	3.2	2.9	3.8	48	<0.1	5.5	4.2	563	2.02	<0.5	3.1	<0.5	5.2	78	<0.1	<0.1	<0.1	36	0.62
G1	Prep Blank		1.2	1.7	3.0	47	<0.1	4.3	4.1	540	1.83	<0.5	2.5	<0.5	4.3	56	<0.1	<0.1	<0.1	35	0.46

QUALITY CONTROL REPORT

SMI08000590.1

Method	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
Analyte	P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	TI	S	Ga	Se	
Unit	%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
MDL	0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5	
Pulp Duplicates																		
REP G1	QC	0.072	6	10	0.56	211	0.117	1	0.98	0.077	0.49	<0.1	<0.01	1.9	0.4	<0.05	5	<0.5
Reference Materials																		
STD DS7	Standard	0.078	12	176	1.03	367	0.126	40	0.96	0.082	0.46	3.7	0.19	2.3	4.1	0.19	5	3.5
STD DS7	Standard	0.077	12	175	1.06	372	0.128	41	1.01	0.093	0.40	3.5	0.19	2.2	4.1	0.19	5	3.6
STD DS7	Standard	0.074	10	184	0.99	348	0.100	39	0.93	0.078	0.44	3.6	0.20	2.1	4.1	0.18	5	3.6
STD DS7	Standard	0.077	13	193	1.07	393	0.114	36	1.01	0.085	0.44	4.0	0.21	2.2	4.1	0.19	5	2.7
STD DS7 Expected		0.08	12.7	163	1.05	370.3	0.124	38.6	0.959	0.073	0.44	3.8	0.2	2.5	4.19	0.21	4.6	3.5
BLK	Blank	<0.001	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
BLK	Blank	<0.001	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
Prep Wash																		
G1	Prep Blank																	
G1	Prep Blank	0.076	9	12	0.58	224	0.131	2	1.26	0.151	0.58	<0.1	<0.01	2.6	0.4	<0.05	5	<0.5
G1	Prep Blank	0.073	6	10	0.58	208	0.117	2	0.96	0.077	0.51	0.1	<0.01	1.9	0.4	<0.05	5	<0.5



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Submitted By: Glen Garratt
 Receiving Lab: Canada-Smithers
 Received: July 10, 2008
 Report Date: July 21, 2008
 Page: 1 of 2

CERTIFICATE OF ANALYSIS

SMI08000601.1

CLIENT JOB INFORMATION

Project: Zymo
 Shipment ID: zy-st-08-01
 P.O. Number
 Number of Samples: 16

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
 DISP-RJT-SOIL Immediate Disposal of Soil Reject

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7
 Canada

CC: Bob Johnston

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status
SS80	16	Dry at 60C sieve 100g to -80 mesh		
Dry at 60C	16	Dry at 60C		
1DX15	15	1:1:1 Aqua Regia digestion ICP-MS analysis	15	Completed

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only. All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.



AcmeLabs ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
Report Date: July 21, 2008

Page: 2 of 2 **Part** 1

CERTIFICATE OF ANALYSIS

SMI08000601.1

Method	Analyte	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
		Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	P
Unit		ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	%	
MDL		0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	0.001
ZXB-08-001	Silt	1.1	33.6	23.3	119	0.2	24.0	16.2	1669	3.99	16.8	2.2	3.2	0.9	78	0.4	1.6	0.1	94	0.62	0.103
ZXB-08-002	Silt	1.4	38.4	74.1	222	0.3	23.0	17.7	3150	4.28	17.0	4.1	6.7	2.4	59	1.0	1.2	0.1	94	0.50	0.181
ZXB-08-003	Silt	3.1	77.9	183.4	471	1.2	24.6	14.2	2990	4.34	124.1	1.8	152.1	1.1	52	2.9	3.8	2.3	50	0.56	0.122
ZXB-08-004	Silt	2.8	174.3	515.2	1134	3.1	42.0	15.8	5472	3.86	124.5	2.2	60.2	0.6	59	8.8	4.0	1.9	40	0.71	0.151
ZXB-08-005	Silt	5.3	158.5	348.2	635	0.9	39.1	17.0	4604	6.00	149.9	2.2	51.7	2.4	45	3.1	4.7	2.9	50	0.55	0.131
ZXB-08-006	Silt	3.0	88.7	464.8	610	2.1	35.2	21.3	4174	5.49	330.6	2.3	63.5	0.8	53	4.5	3.8	4.9	59	0.55	0.145
ZXB-08-007	Silt	9.1	99.0	458.9	760	4.4	34.6	27.7	6041	6.11	302.2	3.6	142.9	1.0	67	5.6	10.8	6.4	37	0.71	0.161
ZXB-08-008	Silt	1.9	84.2	148.7	608	1.6	37.1	17.9	2936	4.66	170.5	1.8	45.0	0.7	48	3.6	2.5	2.3	51	0.47	0.135
ZXB-08-009	Silt	3.0	137.0	334.7	674	2.2	35.9	24.4	5955	6.29	208.0	4.4	52.8	1.3	66	5.3	3.1	3.6	45	0.71	0.155
ZXB-08-010	Silt	2.2	66.9	141.8	668	1.7	45.1	22.8	6217	4.59	434.3	2.0	25.9	0.6	47	6.6	2.0	2.8	42	0.51	0.211
ZXB-08-011	Silt	2.7	76.0	83.2	544	2.5	117.4	20.4	5924	3.43	96.1	2.0	14.1	0.2	58	8.1	2.2	0.8	44	0.56	0.218
ZXR-08-001	Silt	1.1	24.4	12.2	144	0.1	37.0	14.7	1330	3.20	20.7	0.9	3.0	1.0	38	0.6	0.7	0.2	49	0.33	0.072
ZXR-08-002	Silt	0.7	17.9	12.0	114	<0.1	55.1	22.5	3192	4.07	8.1	0.4	2.2	1.3	36	0.3	0.4	0.1	63	0.35	0.075
ZXR-08-003	Silt	1.2	30.8	21.1	220	0.3	29.5	13.4	2307	2.84	28.1	5.5	3.5	0.6	63	1.0	1.2	0.2	42	0.52	0.097
ZXR-08-004	Silt	0.8	29.1	12.9	123	<0.1	26.4	13.1	1104	2.88	16.3	0.6	3.5	1.4	37	0.6	0.6	0.1	47	0.33	0.062
ZXR-08-005	Silt	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.

Vancouver BC V6C 1Z7 Canada

Project:

Zymo

Report Date:

July 21, 2008

Page:

2 of 2

Part 2

CERTIFICATE OF ANALYSIS

SMI08000601.1

Method	Analyte	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
		La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
Unit		ppm	ppm	%	ppm	%	ppm	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
MDL		1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.05	1	0.5	
ZXB-08-001	Silt	13	17	0.46	345	0.035	2	1.83	0.020	0.10	0.2	0.15	5.6	0.1	<0.05	5	0.9
ZXB-08-002	Silt	21	29	0.21	613	0.010	3	1.33	0.009	0.14	0.1	0.06	6.0	0.6	<0.05	3	1.3
ZXB-08-003	Silt	15	6	0.21	331	0.008	3	1.06	0.010	0.09	0.2	0.18	3.8	0.3	0.16	3	1.8
ZXB-08-004	Silt	19	9	0.18	420	0.006	3	1.34	0.009	0.10	0.2	0.63	2.9	0.4	0.17	3	3.4
ZXB-08-005	Silt	18	45	0.29	570	0.007	4	1.38	0.010	0.11	0.4	0.15	5.0	0.4	0.10	4	2.5
ZXB-08-006	Silt	18	17	0.21	336	0.009	3	1.62	0.007	0.08	0.3	0.24	3.9	0.4	0.09	4	3.0
ZXB-08-007	Silt	20	7	0.14	466	0.004	3	1.22	0.007	0.07	0.2	0.59	3.9	1.0	0.24	2	2.6
ZXB-08-008	Silt	17	8	0.19	299	0.006	2	1.67	0.006	0.07	0.1	0.18	3.6	0.3	0.07	3	2.6
ZXB-08-009	Silt	25	8	0.15	577	0.005	3	1.37	0.007	0.08	0.2	0.31	4.4	0.4	0.17	3	2.5
ZXB-08-010	Silt	17	<1	0.17	333	0.005	3	1.90	0.005	0.07	0.2	0.18	2.4	0.5	0.11	3	2.8
ZXB-08-011	Silt	23	5	0.19	349	0.007	3	1.98	0.006	0.07	<0.1	0.24	1.9	0.7	0.09	4	4.6
ZXR-08-001	Silt	5	20	0.13	375	0.004	3	0.68	0.007	0.09	<0.1	0.05	4.3	0.1	<0.05	2	0.6
ZXR-08-002	Silt	4	31	0.64	600	0.004	2	1.79	0.008	0.10	<0.1	0.05	4.8	<0.1	<0.05	5	1.0
ZXR-08-003	Silt	8	9	0.15	347	0.005	4	0.86	0.010	0.08	<0.1	0.71	3.4	0.2	<0.05	2	1.5
ZXR-08-004	Silt	4	23	0.09	265	0.003	2	0.57	0.008	0.11	<0.1	0.05	4.7	0.1	<0.05	1	<0.5
ZXR-08-005	Silt	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.

QUALITY CONTROL REPORT

SMI08000601.1

Method	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	P	
Unit	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	%	
MDL	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	0.001	
Pulp Duplicates																					
ZXB-08-011	Silt	2.7	76.0	83.2	544	2.5	117.4	20.4	5924	3.43	96.1	2.0	14.1	0.2	58	8.1	2.2	0.8	44	0.56	0.218
REP ZXB-08-011	QC	2.4	70.1	84.3	547	2.6	114.5	20.4	5694	3.39	93.3	2.0	9.2	0.3	57	7.7	2.3	0.8	42	0.56	0.225
Reference Materials																					
STD DS7	Standard	22.1	116.6	64.8	406	0.9	56.8	10.3	661	2.48	54.1	4.7	64.3	4.2	70	6.3	5.7	4.3	92	1.00	0.077
STD DS7 Expected		20.92	109	70.6	411	0.89	56	9.7	627	2.39	48.2	4.9	70	4.4	68.7	6.38	5.86	4.51	86	0.93	0.08
BLK	Blank	<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01	<0.001

QUALITY CONTROL REPORT

SMI08000601.1

Method	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
Analyte	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se	
Unit	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
MDL	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5	
Pulp Duplicates																	
ZXB-08-011	Silt	23	5	0.19	349	0.007	3	1.98	0.006	0.07	<0.1	0.24	1.9	0.7	0.09	4	4.6
REP ZXB-08-011	QC	23	5	0.18	344	0.011	4	1.98	0.006	0.08	0.1	0.24	2.2	0.6	0.06	4	3.3
Reference Materials																	
STD DS7	Standard	13	213	1.07	399	0.124	40	1.05	0.091	0.47	3.9	0.20	2.6	4.0	0.19	5	4.9
STD DS7 Expected		12.7	163	1.05	370.3	0.124	38.6	0.959	0.073	0.44	3.8	0.2	2.5	4.19	0.21	4.6	3.5
BLK	Blank	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

ACME ANALYTICAL LABORATORIES LTD.

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.
Vancouver BC V6C 1Z7 Canada

Submitted By:

Glen Garratt

Receiving Lab:

Canada-Smithers

Received:

July 10, 2008

Report Date:

November 20, 2008

Page:

1 of 3

CERTIFICATE OF ANALYSIS

SMI08000602.2

CLIENT JOB INFORMATION

Project: Zymo
Shipment ID: zy-rk-08-03
P.O. Number
Number of Samples: 55

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
DISP-RJT Dispose of Reject After 90 days

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Mincord Exploration Consultants Ltd.
110 - 325 Howe St.
Vancouver BC V6C 1Z7
Canada

CC: Bob Johnston

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status
R150	55	Crush, split and pulverize rock to 200 mesh		
1DX15	55	1:1:1 Aqua Regia digestion ICP-MS analysis	15	Completed
G6	4	Fire Assay Ag by gravimetric finished	30	Completed

ADDITIONAL COMMENTS

Version 2: Group 6 Ag Grav included



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only. All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only. ** asterisk indicates that an analytical result could not be provided due to unusually high levels of interference from other elements.



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project:

Zymo

Report Date:

November 20, 2008

Page:

2 of 3

Part 1

CERTIFICATE OF ANALYSIS

SMI08000602.2

Method Analyte	Unit	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
			Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca
MDL	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%
726531	Rock	6.44	70.7	252.5	1837	8121	7.2	6.0	8.0	>10000	5.62	528.7	0.2	702.3	0.2	70	46.1	66.1	2.7	7	5.02
726532	Rock	1.06	5.2	23.3	750.0	1229	2.1	13.1	15.7	7799	5.42	183.3	0.3	28.1	0.5	21	6.0	6.4	<0.1	25	1.02
726533	Rock	3.70	20.9	3951	8250	>10000	56.4	5.5	14.2	>10000	10.05	1359	0.2	2769	0.2	80	100.8	190.1	33.8	5	5.84
726534	Rock	2.35	0.6	15.5	41.4	160	0.6	9.7	8.7	2192	3.26	20.9	<0.1	3.0	0.4	39	0.5	1.5	<0.1	10	4.48
726535	Rock	2.14	0.7	19.4	78.4	173	0.8	10.1	10.9	4263	3.25	26.5	0.1	4.7	0.4	72	0.8	2.0	0.1	15	11.21
726536	Rock	3.18	1.2	30.0	182.2	820	2.2	4.7	7.4	>10000	5.86	811.9	<0.1	153.0	0.4	8	4.0	6.6	2.5	11	0.31
726537	Rock	2.89	2.6	123.6	2335	5835	10.4	3.4	7.0	>10000	5.88	1834	<0.1	911.5	0.2	79	29.9	8.6	4.1	4	5.70
726538	Rock	2.64	1.6	16.7	44.6	197	0.8	6.1	12.9	1887	4.03	67.5	<0.1	16.0	0.4	38	0.9	9.2	<0.1	18	1.50
726539	Rock	2.66	83.9	66.8	49.5	920	1.0	3.9	8.1	2698	2.97	139.4	0.3	64.8	0.4	3	4.3	15.2	0.1	6	0.08
726540	Rock	2.54	262.4	11.2	105.7	473	0.6	5.0	5.5	4098	2.59	3278	0.5	41.3	0.3	33	2.0	81.7	0.1	8	1.81
726541	Rock	3.15	339.0	60.5	1057	1999	3.4	2.9	2.2	719	3.62	1805	0.6	318.3	0.8	7	10.6	106.4	1.5	2	0.29
726542	Rock	1.84	38.5	6.0	11.4	32	<0.1	4.1	1.9	282	1.19	16.2	<0.1	2.9	0.1	1	<0.1	7.0	<0.1	7	0.02
726543	Rock	2.51	14.8	356.3	101.4	187	1.1	3.1	11.2	1516	3.37	25.7	5.5	68.8	8.8	18	0.4	0.8	3.5	48	0.33
726544	Rock	4.61	11.6	331.9	118.4	143	1.5	3.1	5.6	756	3.35	6.3	3.0	69.1	9.5	17	0.2	0.3	1.6	29	0.18
726545	Rock	4.82	7.8	332.9	59.6	127	0.6	2.9	11.3	1411	3.34	4.5	3.8	50.1	9.9	27	0.4	0.3	0.9	53	0.26
726546	Rock	6.34	6.6	307.4	103.1	127	0.8	3.0	3.9	772	3.05	7.9	3.3	49.1	9.6	14	0.3	0.2	1.2	39	0.23
726547	Rock	5.23	4.6	303.3	112.2	154	1.0	2.3	3.7	580	3.05	5.8	3.9	40.5	9.4	30	0.5	0.4	1.5	49	0.24
726548	Rock	3.13	8.1	794.2	22.3	252	0.7	4.8	6.7	783	5.73	12.5	4.2	79.8	9.0	22	0.2	0.2	0.9	68	0.30
726549	Rock	2.99	7.7	445.0	22.1	201	1.2	3.3	5.7	830	5.76	4.3	4.1	70.9	9.4	14	<0.1	0.3	1.2	66	0.26
726550	Rock	5.16	15.7	982.7	61.1	215	1.9	3.8	8.2	781	4.89	15.9	3.3	143.5	8.1	13	0.7	0.3	1.9	32	0.20
726551	Rock	6.29	13.3	972.6	33.1	175	1.7	3.7	11.3	1469	5.11	12.1	3.3	182.5	8.5	10	0.2	0.5	3.0	36	0.26
726552	Rock	2.25	7.9	955.7	245.0	388	3.6	3.5	7.9	352	4.45	29.6	3.4	131.8	6.6	12	1.8	2.3	10.2	13	0.29
726553	Rock	4.77	11.9	418.0	22.7	107	1.1	3.0	2.8	552	4.79	8.9	2.4	110.9	8.8	13	<0.1	0.4	2.1	42	0.24
726554	Rock	2.98	8.8	502.3	31.3	128	2.4	3.1	4.1	714	5.01	34.8	2.1	217.9	6.6	11	0.2	0.7	7.9	33	0.24
726555	Rock	1.63	22.4	123.1	48.1	143	0.3	4.0	11.4	1856	3.68	58.5	4.6	28.2	4.1	29	0.6	5.9	1.6	20	2.40
726556	Rock	2.72	10.4	298.4	193.1	721	1.7	4.6	10.8	9971	3.54	54.7	4.8	49.1	7.0	55	7.8	2.2	1.2	15	2.66
726557	Rock	2.22	6.2	117.9	20.4	61	0.3	4.5	8.5	381	3.16	5.3	4.2	17.8	5.3	26	0.1	0.1	4.2	17	0.75
726558	Rock	3.33	17.5	575.8	115.5	327	1.4	4.8	12.1	3127	3.02	18.0	5.9	42.5	6.3	50	3.5	0.2	0.8	19	1.76
726559	Rock	2.50	3.4	381.5	10.7	613	0.2	5.4	9.3	1624	2.75	4.2	2.5	13.4	4.6	89	2.9	0.2	0.5	30	2.35
726560	Rock	3.05	4.3	1903	6.3	112	0.8	4.8	9.1	1204	3.17	31.1	3.3	95.4	8.5	62	0.4	1.0	0.4	32	2.05

This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.
Vancouver BC V6C 1Z7 Canada

Project:

Zymo

Report Date:

November 20, 2008

Page:

2 of 3

Part 2

CERTIFICATE OF ANALYSIS

SMI08000602.2

Method	Analyte	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	G6
		P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se	Ag	Ag
Unit		%	ppm	ppm	%	ppm	%	ppm	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	gm/mt
MDL		0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.01	0.1	0.01	0.05	1	0.5	0.5	5	
726531	Rock	0.029	2	4	1.06	35	<0.001	2	0.26	0.005	0.15	0.5	1.76	4.3	0.8	2.95	1	0.7	N.A.	
726532	Rock	0.036	4	9	0.30	83	0.002	5	0.84	0.007	0.32	0.3	0.38	7.0	0.4	0.49	2	<0.5	N.A.	
726533	Rock	0.018	2	3	1.35	16	<0.001	2	0.24	0.005	0.13	0.5	4.30	3.4	0.3	7.94	3	2.0	N.A.	
726534	Rock	0.055	8	5	0.36	74	<0.001	3	0.62	0.018	0.25	<0.1	0.11	4.7	0.2	0.24	1	<0.5	N.A.	
726535	Rock	0.073	8	6	0.60	51	<0.001	1	0.38	0.011	0.20	<0.1	0.09	5.0	0.2	0.40	<1	<0.5	N.A.	
726536	Rock	0.046	3	3	0.30	31	<0.001	3	0.41	0.007	0.22	0.3	0.20	5.2	0.2	1.47	1	<0.5	N.A.	
726537	Rock	0.037	2	3	1.19	20	<0.001	2	0.26	0.006	0.14	0.2	1.24	3.7	0.2	4.26	2	<0.5	N.A.	
726538	Rock	0.085	5	2	0.56	92	<0.001	3	0.52	0.007	0.25	0.4	0.19	6.4	0.2	0.32	<1	0.8	N.A.	
726539	Rock	0.062	6	3	0.02	76	<0.001	3	0.42	0.004	0.24	0.2	0.31	3.9	2.8	0.25	1	0.6	N.A.	
726540	Rock	0.044	3	3	0.50	147	<0.001	3	0.36	0.005	0.20	0.4	15.00	3.5	8.3	0.57	1	0.7	N.A.	
726541	Rock	0.030	1	5	0.07	43	<0.001	1	0.23	0.002	0.14	0.3	5.09	1.3	6.0	2.65	<1	0.7	N.A.	
726542	Rock	0.011	1	17	0.01	21	<0.001	1	0.17	0.002	0.07	<0.1	0.07	1.5	0.3	<0.05	<1	<0.5	N.A.	
726543	Rock	0.159	11	6	0.93	239	0.015	<1	1.69	0.038	0.28	0.1	0.03	3.0	0.5	0.57	6	2.5	N.A.	
726544	Rock	0.142	8	6	0.58	213	0.003	<1	1.23	0.022	0.41	<0.1	0.02	1.8	0.5	0.70	5	3.6	N.A.	
726545	Rock	0.157	13	6	0.98	630	0.005	1	1.75	0.034	0.33	<0.1	<0.01	2.9	0.5	0.18	6	2.0	N.A.	
726546	Rock	0.160	7	6	0.74	353	0.003	1	1.41	0.033	0.34	<0.1	<0.01	2.9	0.5	0.27	5	2.8	N.A.	
726547	Rock	0.184	9	5	0.90	526	0.002	1	1.51	0.032	0.22	<0.1	0.02	3.4	0.4	0.10	6	2.1	N.A.	
726548	Rock	0.151	11	7	1.09	172	0.005	<1	1.82	0.040	0.30	<0.1	<0.01	3.7	0.5	0.67	8	1.8	N.A.	
726549	Rock	0.221	7	4	0.91	142	0.004	1	1.52	0.034	0.27	<0.1	<0.01	4.0	0.4	0.65	8	2.7	N.A.	
726550	Rock	0.161	11	5	0.48	48	0.003	1	1.12	0.027	0.38	<0.1	<0.01	2.0	0.5	1.63	4	3.1	N.A.	
726551	Rock	0.172	10	5	0.57	51	0.003	1	1.18	0.030	0.37	0.1	0.01	2.3	0.5	1.52	5	3.1	N.A.	
726552	Rock	0.164	16	3	0.17	45	0.002	1	0.71	0.016	0.42	0.1	0.08	1.2	0.5	2.60	2	4.1	N.A.	
726553	Rock	0.173	10	5	0.68	241	0.003	<1	1.17	0.028	0.35	0.1	0.01	1.9	0.5	0.62	6	1.8	N.A.	
726554	Rock	0.161	10	5	0.66	58	0.003	1	1.11	0.027	0.31	<0.1	0.02	1.7	0.4	1.61	4	4.1	N.A.	
726555	Rock	0.129	8	3	0.71	28	<0.001	4	0.32	0.012	0.18	0.2	0.02	2.3	0.3	2.51	<1	3.0	N.A.	
726556	Rock	0.168	15	4	0.68	30	<0.001	2	0.41	0.007	0.27	0.2	0.03	2.6	0.6	3.20	1	2.5	N.A.	
726557	Rock	0.101	9	5	0.22	32	<0.001	<1	0.35	0.020	0.23	0.2	0.03	2.0	0.3	2.00	<1	4.2	N.A.	
726558	Rock	0.171	15	4	0.51	40	0.001	3	0.55	0.014	0.30	<0.1	<0.01	2.5	0.5	1.89	1	3.3	N.A.	
726559	Rock	0.153	10	3	0.47	89	<0.001	3	0.40	0.027	0.19	0.1	<0.01	5.9	0.2	0.92	1	0.9	N.A.	
726560	Rock	0.194	19	4	0.56	221	0.002	2	0.53	0.032	0.26	<0.1	<0.01	4.5	0.3	0.48	1	2.1	N.A.	

This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.

Vancouver BC V6C 1Z7 Canada

Project:

Zymo

Report Date:

November 20, 2008

Page:

3 of 3

Part 1

CERTIFICATE OF ANALYSIS

SMI08000602.2

Method	Analyte	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca
Unit	MDL	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%
		0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	0.1	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	0.1	2	0.01
830857	Rock	1.36	3.7	22.8	52.3	126	1.1	5.1	9.3	2764	3.67	31.8	<0.1	7.3	0.4	41	0.4	8.5	<0.1	11	2.24
830858	Rock	1.46	2.2	220.2	2812	1645	9.3	4.4	11.2	>10000	5.97	262.8	<0.1	342.6	0.3	38	9.5	14.4	10.1	10	3.24
830859	Rock	2.27	2.6	>10000	>10000	>10000	>100	2.1	28.3	>10000	15.82	1325	1.7	10584	<0.1	8	950.1	208.6	72.8	<2	0.39
830860	Rock	2.04	23.0	446.7	929.5	>10000	9.9	3.0	6.6	>10000	10.74	847.8	<0.1	3245	<0.1	139	114.4	48.9	3.9	4	9.29
830861	Rock	2.25	6.7	>10000	8374	>10000	71.6	2.4	9.7	>10000	8.73	1195	<0.1	4454	<0.1	721	250.1	248.9	63.1	<2	15.34
830862	Rock	2.84	13.6	2605	4430	>10000	52.9	3.9	72.2	>10000	27.35	2868	0.1	2232	<0.1	50	424.6	90.2	59.0	<2	1.74
830863	Rock	1.83	50.6	>10000	>10000	>10000	>100	3.8	30.3	>10000	18.12	4536	<0.1	17631	<0.1	71	256.8	523.4	309.8	<2	4.02
830864	Rock	2.22	237.0	>10000	5275	>10000	>100	6.2	42.7	>10000	26.27	4187	<0.1	6857	<0.1	26	219.9	>2000	149.0	<2	1.47
830865	Rock	2.14	87.7	5764	1468	>10000	15.2	3.7	7.8	>10000	4.30	1755	0.2	1397	0.2	45	109.2	329.0	7.9	2	3.49
830866	Rock	3.04	324.5	>10000	>10000	>10000	>100	1.0	7.6	>10000	6.62	1392	0.6	2346	0.4	126	1027	>2000	284.6	<2	6.81
830867	Rock	2.39	17.3	3113	>10000	>10000	71.8	4.4	20.7	>10000	11.64	2274	0.4	3173	0.2	72	688.7	323.4	35.4	<2	3.33
830868	Rock	1.58	2.9	91.6	781.9	3114	3.0	6.3	8.5	>10000	6.99	114.7	<0.1	30.7	0.3	38	15.4	17.3	0.7	25	0.66
830869	Rock	1.35	3.2	172.6	847.5	803	5.5	12.9	4.0	255	7.89	833.5	1.6	2512	2.5	16	3.2	22.4	10.9	56	0.04
830870	Rock	1.43	4.9	40.2	641.1	174	3.1	7.8	6.7	198	4.45	199.5	1.9	423.8	8.1	12	0.7	5.9	4.0	6	0.03
830871	Rock	1.45	1.1	13.2	43.2	331	0.3	4.7	2.9	2611	3.80	16.5	4.0	17.6	10.2	55	1.3	1.4	0.9	60	2.24
830872	Rock	1.10	1.9	27.6	188.1	215	1.8	54.5	41.8	902	6.26	169.4	0.1	192.6	0.4	7	1.0	2.1	5.9	13	0.05
830873	Rock	1.49	1.4	23.6	24.2	120	0.2	5.3	5.4	1118	1.75	19.9	5.9	11.5	6.9	106	0.6	1.9	0.3	6	2.44
830874	Rock	2.16	42.3	45.6	260.4	1500	1.6	4.0	5.0	8755	5.01	390.7	<0.1	328.1	0.2	51	9.0	26.7	2.4	3	2.46
830875	Rock	1.44	1.8	14.2	23.1	89	0.2	5.6	4.7	275	2.51	15.1	<0.1	<0.5	0.6	11	0.3	1.6	0.3	5	0.13
830876	Rock	1.56	2.8	21.2	74.7	611	0.5	3.3	4.6	1878	2.39	17.5	5.1	14.0	8.0	102	4.3	1.9	1.0	13	2.79
830877	Rock	1.62	0.8	25.2	24.1	349	0.2	5.9	10.2	2185	6.10	17.6	<0.1	12.5	0.7	24	1.5	0.7	1.2	86	0.91
830878	Rock	1.24	1.4	181.0	169.5	5627	1.8	58.5	19.5	2507	5.06	44.2	2.7	35.6	3.4	20	30.2	1.0	2.7	43	0.42
830879	Rock	0.31	1.6	29.9	1472	4079	1.5	5.6	3.4	7362	3.54	119.7	<0.1	36.5	0.4	42	18.4	26.4	0.2	5	2.24
830880	Rock	0.77	0.6	22.3	30.3	206	0.2	10.7	8.3	859	2.71	36.4	0.1	2.4	0.9	89	0.9	2.4	0.3	15	1.60
830881	Rock	0.78	3.2	121.2	16.0	62	0.4	3.6	6.2	325	3.38	18.8	1.2	85.1	1.8	8	0.3	0.4	5.5	3	0.03



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project:

Zymo

Report Date:

November 20, 2008

Page:

3 of 3

Part 2

CERTIFICATE OF ANALYSIS

SMI08000602.2

Method	Analyte	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	G6
		P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se	Ag	
Unit		%	ppm	ppm	%	ppm	%	ppm	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	gm/mt		
MDL		0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.05	1	0.5	5		
830857	Rock	0.051	5	2	0.68	35	<0.001	2	0.33	0.009	0.19	0.2	0.11	6.3	0.2	0.45	<1	0.8	N.A.	
830858	Rock	0.049	5	3	0.67	57	<0.001	2	0.30	0.011	0.16	0.1	0.21	4.0	0.2	3.02	1	0.6	N.A.	
830859	Rock	0.008	<1	2	0.22	<1	<0.001	2	0.05	0.002	0.02	0.1	13.90	1.1	0.2	>10	26	26.9	568	
830860	Rock	0.019	2	2	2.21	25	<0.001	2	0.15	0.007	0.10	0.2	3.02	4.1	0.3	7.19	2	1.1	N.A.	
830861	Rock	0.008	2	2	1.24	45	<0.001	1	0.08	0.004	0.05	0.2	5.84	1.9	0.1	6.64	2	3.2	N.A.	
830862	Rock	0.006	<1	3	0.49	<1	<0.001	<1	0.10	0.004	0.05	0.2	9.52	1.8	0.2	>10	5	8.0	N.A.	
830863	Rock	0.003	<1	3	1.25	5	<0.001	<1	0.08	0.004	0.05	0.3	7.92	1.9	0.4	>10	5	5.8	236	
830864	Rock	0.022	<1	2	0.48	5	<0.001	<1	0.05	0.002	0.03	0.2	13.38	2.7	1.3	>10	2	4.5	228	
830865	Rock	0.008	2	9	0.69	31	<0.001	1	0.11	0.005	0.05	0.1	1.93	2.9	2.5	1.81	<1	1.0	N.A.	
830866	Rock	0.004	<1	2	1.29	15	<0.001	<1	0.05	0.003	0.03	0.3	36.41	0.8	3.3	>10	3	16.4	295	
830867	Rock	0.022	2	4	0.79	10	<0.001	1	0.14	0.005	0.09	0.9	21.95	1.6	0.6	>10	9	11.2	N.A.	
830868	Rock	0.073	3	6	0.69	41	<0.001	3	0.53	0.015	0.22	1.0	0.79	7.2	0.2	1.23	2	<0.5	N.A.	
830869	Rock	0.140	7	17	0.02	58	<0.001	<1	0.43	0.014	0.13	0.1	0.44	3.2	0.8	0.11	2	3.4	N.A.	
830870	Rock	0.022	9	4	0.02	26	<0.001	1	0.35	0.007	0.24	<0.1	0.16	0.9	0.6	3.17	1	<0.5	N.A.	
830871	Rock	0.163	36	8	1.11	244	0.002	1	2.23	0.046	0.14	0.1	0.04	5.0	0.2	0.16	8	<0.5	N.A.	
830872	Rock	0.019	2	18	0.14	16	<0.001	2	0.23	0.004	0.13	<0.1	0.05	1.2	0.2	5.31	<1	3.8	N.A.	
830873	Rock	0.101	21	3	0.33	344	<0.001	1	0.33	0.028	0.21	0.2	0.26	1.6	0.1	0.25	<1	<0.5	N.A.	
830874	Rock	0.015	1	6	0.49	32	<0.001	1	0.21	0.004	0.14	0.1	0.51	2.5	0.6	3.58	<1	<0.5	N.A.	
830875	Rock	0.047	5	3	0.03	143	<0.001	2	0.34	0.029	0.19	<0.1	0.09	2.9	0.1	0.61	<1	<0.5	N.A.	
830876	Rock	0.122	13	2	0.50	197	0.001	2	0.39	0.016	0.29	0.1	0.23	1.7	0.2	0.66	1	<0.5	N.A.	
830877	Rock	0.123	4	11	1.04	140	0.005	<1	2.53	0.029	0.18	<0.1	0.04	7.8	0.3	0.35	10	<0.5	N.A.	
830878	Rock	0.091	8	17	0.88	37	0.001	2	0.59	0.019	0.16	0.1	0.16	4.1	0.2	2.04	2	1.7	N.A.	
830879	Rock	0.041	5	3	0.47	75	<0.001	2	0.33	0.006	0.17	0.3	0.95	5.2	0.2	1.43	<1	0.5	N.A.	
830880	Rock	0.052	5	5	0.35	100	<0.001	2	0.44	0.031	0.17	0.1	0.12	3.3	0.1	0.69	1	<0.5	N.A.	
830881	Rock	0.012	6	6	0.06	39	<0.001	<1	0.37	0.009	0.22	0.3	0.06	0.4	0.2	2.06	<1	3.5	N.A.	



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.
Vancouver BC V6C 1Z7 Canada

Project:

Zymo

Report Date:

November 20, 2008

Page:

1 of 1

Part 1

QUALITY CONTROL REPORT

SMI08000602.2

Method	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
Unit	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	
MDL	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	
Pulp Duplicates																					
726531	Rock	6.44	70.7	252.5	1837	8121	7.2	6.0	8.0	>10000	5.62	528.7	0.2	702.3	0.2	70	46.1	66.1	2.7	7	5.02
REP 726531	QC		69.4	245.6	1840	7805	7.3	5.2	7.7	>10000	5.57	521.5	0.2	634.5	0.2	70	47.7	68.7	2.8	7	4.75
830867	Rock	2.39	17.3	3113	>10000	>10000	71.8	4.4	20.7	>10000	11.64	2274	0.4	3173	0.2	72	688.7	323.4	35.4	<2	3.33
REP 830867	QC		17.2	3116	>10000	>10000	69.6	4.3	20.8	>10000	11.46	2185	0.3	3063	0.2	67	696.7	319.7	33.5	<2	3.21
830881	Rock	0.78	3.2	121.2	16.0	62	0.4	3.6	6.2	325	3.38	18.8	1.2	85.1	1.8	8	0.3	0.4	5.5	3	0.03
REP 830881	QC		3.0	118.5	16.2	61	0.5	3.5	6.3	319	3.32	18.7	1.1	110.0	1.8	8	0.3	0.4	5.6	3	0.03
Reference Materials																					
STD AGPROOF	Standard																				
STD DS7	Standard		20.9	111.8	70.1	393	0.8	57.6	9.8	631	2.35	50.0	5.0	64.6	4.4	67	6.1	5.7	4.4	89	0.97
STD DS7	Standard		22.0	115.2	70.3	410	0.9	57.7	9.9	641	2.40	50.7	4.9	66.0	4.5	69	6.2	5.8	4.5	90	0.96
STD DS7	Standard		21.3	119.4	76.1	420	0.9	62.2	10.6	659	2.48	51.4	5.5	72.9	4.6	67	6.7	5.7	4.7	93	0.97
STD DS7	Standard		22.2	121.1	72.6	422	0.9	62.4	9.9	658	2.49	52.2	5.1	64.6	4.6	71	6.6	5.9	4.4	92	0.97
STD DS7	Standard		21.0	115.3	64.2	417	0.9	56.4	9.6	639	2.45	54.3	4.8	65.6	3.8	71	6.8	6.3	4.3	91	0.94
STD DS7	Standard		21.5	124.9	71.9	439	0.9	58.5	10.1	663	2.51	55.2	5.3	65.5	4.2	76	6.9	6.5	4.5	90	0.99
STD DS7 Expected			20.9	109	70.6	411	0.9	56	9.7	627	2.39	48.2	4.9	70	4.4	69	6.4	5.9	4.5	86	0.93
STD AGPROOF Expected																					
BLK	Blank		<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01
BLK	Blank		<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01
BLK	Blank		<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01
BLK	Blank																				
BLK	Blank																				
Prep Wash																					
G1	Prep Blank	<0.01	0.7	4.8	3.3	49	<0.1	5.3	4.6	578	1.86	0.6	2.5	4.5	4.7	54	<0.1	<0.1	<0.1	39	0.52
G1	Prep Blank	<0.01	1.3	3.5	3.0	47	<0.1	6.9	4.4	565	1.91	3.3	2.5	2.8	4.5	60	<0.1	<0.1	<0.1	39	0.52



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project:

Zymo

Report Date:

November 20, 2008

Page:

1 of 1

Part 2

QUALITY CONTROL REPORT

SMI08000602.2

Method	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	G6
Analyte	P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se	Ag	
Unit	%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	gm/mt	
MDL	0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5	5	
Pulp Duplicates																			
726531	Rock	0.029	2	4	1.06	35	<0.001	2	0.26	0.005	0.15	0.5	1.76	4.3	0.8	2.95	1	0.7	N.A.
REP 726531	QC	0.028	2	4	1.04	35	<0.001	2	0.26	0.005	0.14	0.4	1.74	4.1	0.8	3.00	1	1.1	
830867	Rock	0.022	2	4	0.79	10	<0.001	1	0.14	0.005	0.09	0.9	21.95	1.6	0.6	>10	9	11.2	N.A.
REP 830867	QC	0.021	2	4	0.78	10	<0.001	<1	0.14	0.004	0.09	0.8	20.98	1.7	0.5	>10	9	9.7	
830881	Rock	0.012	6	6	0.06	39	<0.001	<1	0.37	0.009	0.22	0.3	0.06	0.4	0.2	2.06	<1	3.5	N.A.
REP 830881	QC	0.012	6	5	0.06	41	0.001	<1	0.37	0.009	0.22	0.4	0.06	0.4	0.2	1.99	1	3.4	
Reference Materials																			
STD AGPROOF	Standard																		97
STD DS7	Standard	0.072	12	208	1.04	390	0.118	43	1.04	0.090	0.44	3.7	0.20	2.5	4.3	0.18	5	4.0	
STD DS7	Standard	0.072	12	214	1.05	389	0.122	42	1.03	0.093	0.45	3.8	0.19	2.5	4.2	0.18	4	3.5	
STD DS7	Standard	0.074	12	214	1.09	374	0.117	42	1.05	0.093	0.45	3.9	0.21	2.5	4.5	0.19	5	4.1	
STD DS7	Standard	0.078	13	218	1.09	382	0.122	40	1.04	0.095	0.45	3.8	0.22	2.5	4.3	0.19	5	4.4	
STD DS7	Standard	0.084	12	201	1.09	383	0.127	43	1.02	0.085	0.47	3.6	0.22	2.5	4.0	0.19	5	4.7	
STD DS7	Standard	0.083	13	204	1.13	411	0.135	47	1.06	0.092	0.50	3.8	0.22	2.4	4.5	0.20	5	3.1	
STD DS7 Expected		0.08	13	163	1.05	370	0.124	39	0.959	0.073	0.44	3.8	0.2	2.5	4.2	0.21	4.6	3.5	
STD AGPROOF Expected																			0
BLK	Blank	<0.001	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5	
BLK	Blank	<0.001	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5	
BLK	Blank	<0.001	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5	
BLK	Blank																		<5
BLK	Blank																		<5
Prep Wash																			
G1	Prep Blank	0.074	8	13	0.59	222	0.130	1	1.15	0.088	0.54	0.3	<0.01	2.5	0.4	<0.05	5	<0.5	N.A.
G1	Prep Blank	0.072	8	15	0.60	217	0.123	1	1.08	0.082	0.52	0.4	<0.01	2.2	0.4	<0.05	5	<0.5	N.A.



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.

Vancouver BC V6C 1Z7 Canada

Submitted By:

Glen Garratt

Receiving Lab:

Canada-Smithers

Received:

July 12, 2008

Report Date:

July 28, 2008

Page:

1 of 3

CERTIFICATE OF ANALYSIS

SMI08000612.1

CLIENT JOB INFORMATION

Project: Zymo
Shipment ID: zy-rk-08-04
P.O. Number
Number of Samples: 38

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
DISP-RJT Dispose of Reject After 90 days

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Mincord Exploration Consultants Ltd.
110 - 325 Howe St.
Vancouver BC V6C 1Z7
Canada

CC: Bob Johnston

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status
R150	38	Crush, split and pulverize rock to 200 mesh		
1DX15	38	1:1:1 Aqua Regia digestion ICP-MS analysis	15	Completed

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only. All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**

110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo

Report Date: July 28, 2008

Page: 2 of 3 Part 1

CERTIFICATE OF ANALYSIS

SMI08000612.1

Method	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
Unit	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	ppm	
MDL	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	
726561	Rock	0.16	5.0	224.2	17.8	71	0.1	7.1	6.7	565	2.28	2.0	3.6	10.9	9.5	26	0.3	0.2	0.4	30	1.14
726562	Rock	4.56	5.2	1976	111.2	739	2.1	2.7	14.2	5611	2.92	15.1	4.7	85.4	7.9	19	4.2	0.9	0.9	14	0.99
726563	Rock	2.80	4.3	729.2	408.5	770	3.1	4.4	9.5	6122	3.08	23.2	5.4	32.5	9.8	14	11.2	1.9	0.6	14	0.42
726564	Rock	2.30	21.2	345.8	721.6	176	9.9	2.6	8.4	1518	3.66	127.3	3.7	97.4	8.2	10	2.2	17.6	1.1	14	0.24
726565	Rock	2.73	9.1	562.9	38.1	377	1.0	3.8	12.6	2439	3.60	4.9	4.4	40.6	9.8	39	1.8	0.2	2.0	21	0.90
726566	Rock	1.84	15.3	195.3	19.5	55	0.3	4.3	9.9	1113	2.49	4.9	3.3	8.4	8.2	74	0.1	0.3	1.1	25	2.33
726567	Rock	2.49	4.4	101.6	7.7	70	<0.1	5.8	9.9	690	2.97	3.1	2.5	7.1	8.9	75	0.3	0.2	1.1	32	1.17
726568	Rock	2.19	2.2	114.9	69.1	123	0.5	5.6	14.2	1983	3.17	11.8	4.3	39.0	8.7	52	0.6	0.4	3.5	49	2.22
726569	Rock	2.57	1.4	97.6	27.3	109	0.6	5.2	10.8	896	3.35	51.1	4.6	41.9	6.7	61	0.3	0.4	5.3	25	2.33
726570	Rock	2.17	2.2	154.9	70.0	278	0.7	4.8	9.2	1511	2.94	7.6	5.6	35.2	7.3	56	1.6	0.2	3.5	36	2.63
726571	Rock	2.34	4.0	297.4	35.6	67	0.7	4.8	9.6	384	4.86	34.3	5.4	37.8	8.7	14	0.3	0.4	1.5	5	0.71
726572	Rock	2.42	18.3	1585	30.1	269	1.6	3.9	10.2	675	3.93	429.9	3.9	78.1	3.5	34	2.1	175.2	1.6	15	1.96
726573	Rock	2.99	8.8	1171	12.1	93	0.7	5.3	12.2	1481	3.73	110.5	3.4	99.4	2.9	69	0.4	3.3	0.3	42	3.09
726574	Rock	5.39	24.5	611.6	67.0	83	1.6	2.5	7.9	105	4.08	340.3	2.5	154.7	4.9	10	0.9	11.4	0.7	22	0.14
726575	Rock	2.91	18.2	997.6	44.6	72	2.4	5.5	10.8	619	4.45	171.4	3.7	457.4	5.1	42	0.4	9.4	0.2	9	0.80
726576	Rock	2.59	1.7	75.3	3.3	61	<0.1	4.2	7.4	693	3.60	2.5	1.8	8.8	4.6	22	0.2	0.3	<0.1	47	0.36
726577	Rock	3.03	53.2	625.2	5.8	44	0.6	4.4	7.5	116	3.32	308.0	2.3	103.7	6.0	21	<0.1	181.6	0.8	15	0.12
726578	Rock	2.53	11.4	189.8	37.8	91	2.7	1.5	2.2	73	2.52	11.2	2.2	124.1	6.6	16	0.2	1.2	3.1	10	0.01
726579	Rock	2.29	4.1	119.8	5.1	68	0.5	3.4	2.9	59	3.64	4.2	3.8	48.0	9.3	18	<0.1	1.3	1.4	14	0.03
726580	Rock	2.82	3.5	367.6	40.2	90	0.5	2.9	5.6	236	3.51	4.4	4.2	59.0	10.4	41	0.4	0.3	1.0	16	0.17
830882	Rock	1.20	0.7	19.8	7.0	179	<0.1	7.5	6.7	543	4.58	9.4	<0.1	<0.5	0.6	23	0.4	1.7	<0.1	25	1.13
830883	Rock	1.23	37.7	3501	609.1	>10000	34.4	4.0	17.6	2331	3.64	75.2	<0.1	57.5	0.4	13	568.4	489.9	40.4	3	0.66
830884	Rock	1.32	4.9	>10000	4053	>10000	>100	15.7	305.9	6660	19.35	3477	<0.1	871.5	<0.1	11	881.1	121.3	157.1	14	0.45
830885	Rock	1.19	4.2	39.1	16.1	393	0.3	7.6	5.0	639	2.14	13.2	<0.1	<0.5	0.5	45	2.1	4.0	0.3	5	0.88
830886	Rock	1.23	2.0	40.2	157.1	513	0.3	10.9	9.7	811	3.37	21.2	0.1	<0.5	0.7	48	2.4	1.4	0.3	8	1.96
830887	Rock	1.46	1.2	5.4	15.7	107	0.3	5.1	6.8	821	3.14	17.4	<0.1	8.9	0.5	33	0.4	1.4	<0.1	13	0.98
830888	Rock	1.61	4.4	17.2	4.8	117	0.1	8.4	6.6	1029	3.66	50.9	0.1	2.2	0.8	25	0.5	1.3	0.4	43	1.28
830889	Rock	1.12	0.5	128.0	19.9	67	0.6	9.2	23.3	1880	12.51	51.1	0.1	14.8	0.4	236	0.2	4.4	4.4	24	7.27
830890	Rock	1.37	3.3	142.3	84.4	105	1.9	7.8	7.7	1133	5.36	185.9	<0.1	24.0	0.7	17	0.5	11.2	5.0	5	0.94
830891	Rock	1.49	43.0	273.0	769.0	131	8.4	0.7	0.7	58	17.14	6179	0.3	828.8	0.9	4	0.2	449.0	544.7	12	0.04



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
 Report Date: July 28, 2008

Page: 2 of 3 Part 2

CERTIFICATE OF ANALYSIS

SMI08000612.1

Method	Analyte	Unit	MDL	1DX15 P	1DX15 La	1DX15 Cr	1DX15 Mg	1DX15 Ba	1DX15 Ti	1DX15 B	1DX15 Al	1DX15 Na	1DX15 K	1DX15 W	1DX15 Hg	1DX15 Sc	1DX15 Ti	1DX15 S	1DX15 Ga	1DX15 Se
				%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm
				0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5
726561	Rock			0.145	25	6	0.13	126	0.001	2	0.54	0.029	0.25	0.1	0.02	3.2	0.3	0.82	1	1.0
726562	Rock			0.162	19	3	0.22	79	0.001	2	0.34	0.005	0.19	0.2	0.04	2.5	0.4	1.10	<1	3.0
726563	Rock			0.164	26	4	0.05	216	0.001	2	0.46	0.006	0.29	0.1	0.03	2.3	0.6	0.52	1	1.5
726564	Rock			0.148	22	3	0.06	62	<0.001	2	0.33	0.002	0.21	0.2	0.12	1.3	0.5	1.43	<1	3.6
726565	Rock			0.165	19	3	0.22	66	0.001	2	0.48	0.021	0.24	<0.1	<0.01	3.6	0.5	1.42	1	3.5
726566	Rock			0.146	31	4	0.50	44	0.001	<1	0.57	0.016	0.17	0.3	<0.01	1.9	0.3	2.04	2	3.6
726567	Rock			0.134	17	5	0.58	35	0.001	<1	0.74	0.057	0.24	<0.1	<0.01	3.6	0.3	2.20	3	4.2
726568	Rock			0.164	26	5	0.86	49	0.002	2	0.90	0.024	0.17	<0.1	<0.01	4.4	0.2	2.44	4	0.7
726569	Rock			0.144	7	3	0.71	25	0.001	3	0.45	0.025	0.20	<0.1	0.01	3.4	0.3	3.24	1	1.0
726570	Rock			0.175	14	3	0.91	37	0.002	3	0.62	0.018	0.19	<0.1	<0.01	4.5	0.3	2.14	2	1.2
726571	Rock			0.117	9	3	0.31	25	0.002	2	0.63	0.011	0.38	0.1	0.03	1.1	0.5	5.16	2	4.4
726572	Rock			0.100	5	3	0.62	31	<0.001	3	0.52	0.006	0.29	0.5	0.04	2.2	0.3	2.70	1	2.8
726573	Rock			0.124	5	3	1.08	43	<0.001	5	0.62	0.009	0.27	0.2	0.16	5.0	0.6	1.74	2	1.5
726574	Rock			0.158	8	4	0.05	37	0.001	2	0.49	0.004	0.29	0.3	0.24	2.6	1.6	2.28	1	2.3
726575	Rock			0.073	8	4	0.31	15	<0.001	4	0.61	0.009	0.38	1.0	0.21	1.3	1.6	4.50	2	3.2
726576	Rock			0.123	17	5	0.14	299	0.009	<1	0.68	0.029	0.20	0.2	0.10	4.7	0.2	<0.05	3	<0.5
726577	Rock			0.085	12	6	0.15	80	0.002	3	0.73	0.013	0.50	0.5	0.08	1.3	0.4	1.46	2	3.7
726578	Rock			0.067	22	4	0.08	208	0.002	<1	0.45	0.008	0.41	0.2	0.16	1.0	0.4	0.64	2	2.6
726579	Rock			0.131	34	5	0.09	208	0.001	1	0.71	0.011	0.45	0.2	0.02	1.1	0.3	0.66	2	2.2
726580	Rock			0.142	28	4	0.14	166	0.002	<1	0.68	0.018	0.40	0.1	<0.01	1.8	0.4	0.93	2	1.4
830882	Rock			0.032	8	10	0.79	90	0.001	2	1.88	0.024	0.15	0.1	0.13	5.8	<0.1	0.17	6	<0.5
830883	Rock			0.012	2	3	0.16	45	<0.001	2	0.21	0.004	0.12	0.2	7.46	1.9	0.6	3.16	1	4.7
830884	Rock			0.014	1	4	0.49	13	0.001	2	0.64	0.007	0.12	2.2	22.20	4.4	1.0	>10	3	8.8
830885	Rock			0.035	4	2	0.37	90	<0.001	1	0.33	0.008	0.13	0.3	0.12	3.5	0.2	0.68	<1	<0.5
830886	Rock			0.074	7	5	0.21	141	0.002	2	0.77	0.027	0.21	<0.1	0.11	3.6	0.1	0.96	2	<0.5
830887	Rock			0.042	5	5	0.81	96	0.001	2	1.37	0.027	0.13	<0.1	0.04	3.5	<0.1	0.72	5	<0.5
830888	Rock			0.060	6	15	0.70	69	0.002	1	1.60	0.079	0.14	<0.1	0.26	5.5	0.2	0.37	7	0.7
830889	Rock			0.180	6	6	1.65	40	0.001	1	0.79	0.016	0.11	0.2	0.19	4.1	0.3	5.35	3	1.0
830890	Rock			0.029	1	4	0.33	48	<0.001	2	0.40	0.007	0.31	0.1	0.34	1.6	0.5	3.41	1	1.2
830891	Rock			0.139	3	3	0.01	108	<0.001	1	0.25	0.004	0.19	1.0	3.68	1.0	1.7	0.48	1	11.0

This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.

Vancouver BC V6C 1Z7 Canada

Project:

Zymo

Report Date:

July 28, 2008

Page:

3 of 3

Part 1

CERTIFICATE OF ANALYSIS

SMI08000612.1

Method	Analyte	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca
Unit		kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%
MDL		0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01
830892	Rock	1.33	1.2	108.4	32.3	70	0.4	8.3	13.7	1194	7.21	3356	<0.1	14.5	0.5	58	0.2	31.1	2.8	38	1.66
830893	Rock	2.01	2.1	63.6	12.4	57	0.3	9.1	5.0	559	5.53	27.9	3.3	26.1	7.2	75	0.2	2.5	6.9	24	1.64
830894	Rock	0.88	1.8	6.8	45.5	44	0.7	26.5	12.1	92	3.94	250.1	<0.1	81.1	0.3	21	0.1	3.4	0.6	4	0.03
830895	Rock	0.80	3.2	186.1	17.5	84	0.4	6.4	6.4	903	8.60	21.9	<0.1	56.7	0.4	6	0.2	3.4	3.1	50	0.25
830896	Rock	1.35	4.6	34.2	13.6	74	0.4	13.3	9.8	718	5.94	311.7	6.1	20.2	8.9	13	0.3	0.8	3.1	16	0.53
830897	Rock	1.48	0.8	12.2	7.9	184	0.1	9.7	7.6	612	3.50	2.3	<0.1	0.8	0.5	27	0.8	0.2	0.7	48	1.96
830898	Rock	1.22	2.2	16.0	5.9	57	<0.1	5.2	9.2	768	3.94	5.1	1.8	6.0	5.1	62	<0.1	0.1	0.2	91	1.50
830899	Rock	1.20	1.4	43.3	12.6	27	<0.1	1.0	4.0	199	6.21	10.7	0.4	4.1	2.6	13	<0.1	1.3	1.3	133	0.10



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
Report Date: July 28, 2008

Page: 3 of 3 **Part** 2

CERTIFICATE OF ANALYSIS

SMI08000612.1

Method	Analyte	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
		P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
Unit		%	ppm	ppm	%	ppm	%	ppm	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm
MDL		0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.05	1	0.5	0.5
830892	Rock	0.125	4	7	1.16	52	0.002	6	0.70	0.009	0.47	0.4	1.10	7.9	0.8	1.77	2	<0.5
830893	Rock	0.161	15	5	0.58	22	0.002	1	0.55	0.018	0.22	0.3	0.13	3.7	0.3	3.43	2	1.0
830894	Rock	0.019	1	11	<0.01	27	<0.001	2	0.14	0.004	0.08	<0.1	0.03	1.1	0.2	3.08	<1	0.7
830895	Rock	0.115	3	7	0.70	39	0.002	1	1.35	0.006	0.32	0.2	0.15	7.4	0.4	4.09	6	<0.5
830896	Rock	0.147	7	8	0.28	18	<0.001	2	0.44	0.007	0.27	0.1	0.15	1.7	0.4	4.85	1	2.9
830897	Rock	0.032	4	16	0.83	69	0.002	1	1.13	0.027	0.16	<0.1	0.03	4.7	<0.1	0.95	4	<0.5
830898	Rock	0.148	20	7	1.11	170	0.082	2	1.93	0.084	0.12	0.2	0.02	4.8	0.1	0.23	9	<0.5
830899	Rock	0.137	5	2	1.82	153	0.002	<1	2.42	0.013	0.18	<0.1	0.02	5.6	0.3	0.86	8	2.6

QUALITY CONTROL REPORT

SMI08000612.1

Method	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
Unit	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	
MDL	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	
Pulp Duplicates																					
830888	Rock	1.61	4.4	17.2	4.8	117	0.1	8.4	6.6	1029	3.66	50.9	0.1	2.2	0.8	25	0.5	1.3	0.4	43	1.28
REP 830888	QC		5.1	16.7	4.9	111	0.1	7.7	6.7	1042	3.71	51.6	0.1	2.2	0.8	25	0.5	1.4	0.4	44	1.32
830899	Rock	1.20	1.4	43.3	12.6	27	<0.1	1.0	4.0	199	6.21	10.7	0.4	4.1	2.6	13	<0.1	1.3	1.3	133	0.10
REP 830899	QC		1.4	46.0	13.5	27	0.1	1.0	4.0	202	6.39	10.8	0.5	10.9	2.8	14	<0.1	1.3	1.3	135	0.10
Reference Materials																					
STD DS7	Standard		19.4	108.2	68.2	393	0.8	55.2	8.9	608	2.30	50.3	4.9	57.6	4.0	62	6.1	5.6	4.3	83	0.87
STD DS7	Standard		22.3	116.6	69.4	413	0.8	58.2	9.9	663	2.43	53.9	5.0	71.3	4.5	72	6.3	5.8	4.4	90	0.98
STD DS7	Standard		21.0	119.2	71.5	424	0.9	59.9	10.0	642	2.43	51.3	5.1	69.9	4.2	62	6.4	6.1	4.6	89	0.95
STD DS7	Standard		22.1	118.4	70.6	429	0.9	58.9	9.8	657	2.44	53.1	5.1	76.8	4.4	68	6.5	6.3	4.5	91	0.95
STD DS7 Expected			20.9	109	70.6	411	0.9	56	9.7	627	2.39	48.2	4.9	70	4.4	69	6.4	5.9	4.5	86	0.93
BLK	Blank		<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01
BLK	Blank		<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01
Prep Wash																					
G1	Prep Blank	<0.01	3.6	2.9	2.7	46	<0.1	5.5	4.0	556	1.88	<0.5	2.2	<0.5	3.7	52	<0.1	0.1	<0.1	37	0.43
G1	Prep Blank	<0.01	1.1	2.4	2.4	48	<0.1	4.6	4.3	539	1.77	<0.5	2.3	<0.5	3.7	38	<0.1	0.1	<0.1	36	0.37



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.

Vancouver BC V6C 1Z7 Canada

Project:

Zymo

Report Date:

July 28, 2008

Page:

1 of 1

Part 2

QUALITY CONTROL REPORT

SMI08000612.1

Method		1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
Analyte		P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se	
Unit		%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
MDL		0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5	
Pulp Duplicates																			
830888	Rock	0.060	6	15	0.70	69	0.002	1	1.60	0.079	0.14	<0.1	0.26	5.5	0.2	0.37	7	0.7	
REP 830888	QC	0.061	6	15	0.70	71	0.002	1	1.66	0.071	0.14	<0.1	0.26	5.5	0.2	0.39	7	0.6	
830899	Rock	0.137	5	2	1.82	153	0.002	<1	2.42	0.013	0.18	<0.1	0.02	5.6	0.3	0.86	8	2.6	
REP 830899	QC	0.140	5	2	1.89	157	0.002	1	2.46	0.014	0.18	<0.1	0.02	5.9	0.3	0.87	9	2.4	
Reference Materials																			
STD DS7	Standard	0.077	11	194	1.02	353	0.103	42	0.95	0.087	0.46	3.8	0.20	2.2	4.1	0.17	5	3.6	
STD DS7	Standard	0.076	13	210	1.06	396	0.116	40	1.05	0.091	0.49	4.2	0.19	2.4	4.5	0.18	5	4.4	
STD DS7	Standard	0.079	12	199	1.07	365	0.109	43	1.01	0.086	0.46	3.7	0.22	2.3	4.4	0.20	5	3.5	
STD DS7	Standard	0.081	13	208	1.06	380	0.112	42	1.02	0.090	0.47	4.2	0.22	2.5	4.7	0.19	5	4.2	
STD DS7 Expected		0.08	13	163	1.05	370	0.124	39	0.959	0.073	0.44	3.8	0.2	2.5	4.2	0.21	4.6	3.5	
BLK	Blank	<0.001	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5	
BLK	Blank	<0.001	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5	
Prep Wash																			
G1	Prep Blank	0.074	6	12	0.58	205	0.110	1	1.01	0.083	0.51	0.4	<0.01	2.5	0.4	<0.05	5	<0.5	
G1	Prep Blank	0.077	5	11	0.60	209	0.105	<1	0.88	0.051	0.49	0.2	<0.01	1.8	0.4	<0.05	5	<0.5	



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Submitted By: Glen Garratt
 Receiving Lab: Canada-Smithers
 Received: July 14, 2008
 Report Date: July 25, 2008
 Page: 1 of 2

CERTIFICATE OF ANALYSIS

SMI08000615.1

CLIENT JOB INFORMATION

Project: Zymo
 Shipment ID: zy-st-08-02
 P.O. Number
 Number of Samples: 17

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
 DISP-RJT-SOIL Immediate Disposal of Soil Reject

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7
 Canada

CC: Bob Johnston

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status
SS80	17	Dry at 60C sieve 100g to -80 mesh		
Dry at 60C	17	Dry at 60C		
1DX15	17	1:1:1 Aqua Regia digestion ICP-MS analysis	15	Completed

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only. All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
Report Date: July 25, 2008

Page: 2 of 2 **Part** 1

CERTIFICATE OF ANALYSIS

SMI08000615.1

Method	Analyte	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
		Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	P
Unit		ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	%	
MDL		0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	0.001
ZXR-08-005	Silt	1.9	26.3	35.5	581	0.6	51.2	27.8	>10000	4.65	29.6	2.9	2.6	0.4	78	7.2	1.7	0.1	51	0.74	0.136
ZXR-08-006	Silt	1.4	14.6	33.3	241	0.1	14.8	12.0	2616	2.85	15.8	0.9	2.6	0.7	32	1.1	1.2	0.1	52	0.25	0.062
ZXR-08-007	Silt	2.1	31.1	80.1	411	0.5	18.2	18.0	4601	3.90	24.2	2.1	5.2	0.5	49	3.1	1.3	0.2	59	0.44	0.122
ZXR-08-008	Silt	1.6	50.8	79.3	255	0.8	27.2	14.3	1756	3.78	52.7	1.0	18.5	1.4	43	1.3	2.6	0.6	53	0.50	0.077
ZXR-08-009	Silt	1.4	42.0	114.7	414	0.8	13.6	9.3	2455	2.64	43.6	1.2	17.8	1.3	13	1.4	1.7	0.9	34	0.13	0.064
ZXR-08-010	Silt	1.5	52.3	174.5	348	3.3	13.9	9.0	2592	3.07	49.5	1.9	24.8	0.5	31	2.0	1.7	1.5	42	0.37	0.117
ZXR-08-011	Silt	2.9	75.7	69.0	437	0.6	42.8	22.6	8178	4.30	49.8	1.7	13.0	0.7	33	4.5	2.3	1.2	47	0.29	0.103
ZXR-08-012	Silt	1.5	38.2	126.2	404	1.2	16.5	14.7	4754	3.07	68.0	1.3	15.9	0.7	31	3.4	1.8	1.2	40	0.33	0.088
ZXR-08-013	Silt	1.5	34.3	65.7	296	0.4	18.7	11.9	1812	3.07	40.8	0.8	8.8	1.4	33	1.3	2.0	0.5	45	0.32	0.071
ZXR-08-014	Silt	3.1	38.2	78.1	335	0.4	16.3	13.2	2899	3.28	84.6	0.9	11.6	0.9	30	1.7	3.1	0.6	41	0.25	0.072
ZXR-08-015	Silt	2.0	61.6	99.6	456	0.6	16.0	12.4	3512	4.11	261.0	1.0	24.6	0.7	38	2.9	6.0	1.4	34	0.31	0.088
ZXR-08-016	Silt	4.5	75.8	92.5	451	0.8	12.9	12.2	2234	3.88	191.2	0.6	43.2	1.1	22	3.1	10.4	3.3	23	0.25	0.069
ZXR-08-017	Silt	1.9	32.2	71.5	242	0.7	13.3	13.4	2241	3.26	69.7	0.7	14.8	0.6	20	0.8	3.4	0.6	43	0.23	0.070
ZXR-08-018	Silt	4.3	162.8	124.2	453	0.7	20.4	24.4	4463	7.01	804.1	1.0	120.2	1.2	41	3.4	29.9	6.2	28	0.36	0.093
ZXR-08-019	Silt	2.5	61.4	57.5	252	0.3	18.5	13.4	1561	3.92	47.2	0.6	10.3	1.1	16	1.3	1.9	0.6	38	0.22	0.059
ZXR-08-020	Silt	3.2	78.5	53.3	211	0.3	13.6	12.3	1122	3.81	49.4	0.6	11.3	1.0	14	0.5	1.9	0.6	40	0.18	0.063
ZXR-08-021	Silt	2.0	55.9	59.6	205	0.5	16.5	13.1	1482	3.50	43.3	0.6	9.9	0.6	27	0.8	2.2	0.5	43	0.33	0.066



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
 Report Date: July 25, 2008

Page: 2 of 2 Part 2

CERTIFICATE OF ANALYSIS

SMI08000615.1

Method	Analyte	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
		La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
		ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm
		MDL	MDL	MDL	MDL	MDL	MDL	MDL	MDL	MDL	MDL	MDL	MDL	MDL	MDL	MDL	MDL
ZXR-08-005	Silt	19	5	0.26	922	0.009	2	1.54	0.016	0.05	0.1	0.19	3.7	0.6	0.06	3	1.9
ZXR-08-006	Silt	8	10	0.26	224	0.014	2	1.07	0.016	0.04	0.2	0.11	2.9	0.2	<0.05	3	<0.5
ZXR-08-007	Silt	15	9	0.24	372	0.009	2	1.70	0.009	0.05	0.1	0.14	3.5	0.4	<0.05	3	1.8
ZXR-08-008	Silt	10	12	0.31	199	0.021	2	0.70	0.020	0.06	<0.1	0.10	5.0	0.1	0.27	2	0.8
ZXR-08-009	Silt	10	7	0.13	130	0.007	<1	0.84	0.004	0.04	<0.1	0.05	2.5	0.2	<0.05	2	0.9
ZXR-08-010	Silt	16	4	0.15	254	0.004	2	1.17	0.005	0.05	0.1	0.17	2.4	0.3	<0.05	3	1.3
ZXR-08-011	Silt	11	12	0.25	358	0.007	3	1.34	0.005	0.07	<0.1	0.12	3.7	0.5	<0.05	3	1.1
ZXR-08-012	Silt	11	6	0.17	227	0.006	2	1.21	0.005	0.05	<0.1	0.12	2.4	0.3	0.06	3	1.0
ZXR-08-013	Silt	8	11	0.28	139	0.020	2	0.77	0.020	0.06	0.1	0.05	3.7	0.1	0.14	2	<0.5
ZXR-08-014	Silt	10	10	0.19	173	0.008	2	1.00	0.005	0.05	0.2	0.11	3.0	0.3	<0.05	3	0.9
ZXR-08-015	Silt	10	6	0.16	202	0.005	2	0.91	0.005	0.05	0.2	0.23	2.8	0.3	<0.05	2	1.1
ZXR-08-016	Silt	9	7	0.18	174	0.003	2	0.68	0.007	0.05	0.3	0.26	3.1	0.2	0.15	2	0.9
ZXR-08-017	Silt	12	9	0.15	132	0.008	3	1.56	0.005	0.04	0.1	0.19	3.2	0.2	<0.05	3	1.1
ZXR-08-018	Silt	10	9	0.15	275	0.005	3	0.83	0.007	0.05	0.4	0.76	3.1	0.6	0.09	2	2.0
ZXR-08-019	Silt	8	11	0.26	139	0.005	<1	0.87	0.005	0.04	<0.1	0.06	3.7	0.1	<0.05	3	0.8
ZXR-08-020	Silt	7	10	0.27	109	0.005	1	1.09	0.005	0.04	<0.1	0.06	3.5	0.1	0.06	3	0.9
ZXR-08-021	Silt	9	13	0.23	140	0.007	1	1.33	0.006	0.05	<0.1	0.10	2.7	0.1	<0.05	3	1.4

QUALITY CONTROL REPORT

SMI08000615.1

Method	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	P	
Unit	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	%	
MDL	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	0.001	
Reference Materials																					
STD DS7	Standard	18.5	102.3	58.8	386	0.8	52.7	8.4	576	2.28	50.1	4.0	73.5	3.8	61	5.6	5.5	4.0	81	0.86	0.070
STD DS7 Expected		20.92	109	70.6	411	0.89	56	9.7	627	2.39	48.2	4.9	70	4.4	68.7	6.38	5.86	4.51	86	0.93	0.08
BLK	Blank	<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01	<0.001

QUALITY CONTROL REPORT

SMI08000615.1

Method	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
Analyte	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se	
Unit	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
MDL	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5	
Reference Materials																	
STD DS7	Standard	11	184	0.96	357	0.106	34	0.91	0.074	0.42	3.5	0.19	2.2	4.0	0.22	5	3.6
STD DS7 Expected		12.7	163	1.05	370.3	0.124	38.6	0.959	0.073	0.44	3.8	0.2	2.5	4.19	0.21	4.6	3.5
BLK	Blank	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.

Vancouver BC V6C 1Z7 Canada

Submitted By:

Glen Garratt

Receiving Lab:

Canada-Smithers

Received:

July 14, 2008

Report Date:

August 04, 2008

Page:

1 of 3

CERTIFICATE OF ANALYSIS

SMI08000616.1

CLIENT JOB INFORMATION

Project: Zymo
Shipment ID: zy-rk-08-05
P.O. Number
Number of Samples: 44

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
DISP-RJT Dispose of Reject After 90 days

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Mincord Exploration Consultants Ltd.
110 - 325 Howe St.
Vancouver BC V6C 1Z7
Canada

CC: Bob Johnston

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status
R150	44	Crush, split and pulverize rock to 200 mesh		
1DX15	44	1:1:1 Aqua Regia digestion ICP-MS analysis	15	Completed

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only. All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
 Report Date: August 04, 2008

Page: 2 of 3 Part 1

CERTIFICATE OF ANALYSIS

SMI08000616.1

Method	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
Unit	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	
MDL	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	
726581	Rock	1.76	2.3	6.9	48.8	27	<0.1	12.9	12.4	375	2.37	18.4	0.1	4.1	1.2	22	<0.1	0.1	0.7	37	0.53
726582	Rock	4.78	1.1	743.3	22.2	39	0.3	8.5	64.2	714	27.18	2.2	<0.1	47.9	0.3	8	<0.1	1.0	8.8	50	0.50
726583	Rock	2.23	1.2	54.1	7.6	36	<0.1	8.7	11.8	592	5.27	3.1	0.1	9.6	1.1	25	<0.1	1.2	0.5	51	0.28
726584	Rock	2.08	1.4	74.9	9.0	31	<0.1	10.0	18.3	644	5.55	34.0	0.1	4.2	0.9	29	<0.1	4.7	0.4	47	0.41
726585	Rock	2.81	2.0	210.2	18.0	47	0.2	6.5	23.1	1016	13.82	88.6	0.1	9.5	1.0	12	<0.1	12.4	1.6	119	0.19
726586	Rock	3.06	1.4	99.3	16.3	21	0.1	2.5	4.8	379	16.98	0.9	0.1	23.1	0.8	10	<0.1	2.0	1.6	108	0.06
726587	Rock	1.69	1.0	56.1	11.0	26	<0.1	2.9	9.3	728	4.48	2.2	0.2	3.0	1.3	791	0.1	0.8	0.8	26	11.48
726588	Rock	3.04	2.0	86.0	22.1	65	0.1	6.7	21.2	484	5.88	4.9	0.5	18.7	3.5	132	0.3	1.6	1.0	100	2.40
726589	Rock	5.05	1.8	812.8	30.1	44	0.7	15.9	63.0	218	20.07	12.8	0.3	12.7	0.6	8	0.1	1.6	18.0	77	0.14
726590	Rock	5.17	2.8	188.8	13.2	43	<0.1	6.2	18.1	327	6.25	2.3	0.7	33.9	4.1	156	0.2	0.2	1.0	112	1.79
726591	Rock	2.84	2.9	39.3	3.7	11	<0.1	3.1	6.5	139	1.42	1.3	0.2	114.8	0.5	40	<0.1	0.1	1.1	8	1.61
726592	Rock	2.28	3.9	15.0	7.0	6	<0.1	5.0	9.1	121	8.32	7.8	1.4	57.9	0.4	933	<0.1	0.4	0.9	6	1.01
726593	Rock	3.73	4.6	24.0	7.9	12	<0.1	5.4	18.4	284	4.30	8.4	0.6	9.3	4.0	76	<0.1	0.5	0.2	8	2.31
726594	Rock	2.33	1.2	26.6	3.5	22	<0.1	10.8	5.3	293	1.66	2.6	0.1	4.9	1.0	43	0.2	0.3	0.1	8	1.16
726595	Rock	2.09	14.8	172.5	4.9	29	0.1	12.5	16.2	605	2.38	4.1	0.2	7.3	1.2	40	0.2	1.3	0.1	18	1.15
726596	Rock	2.59	8.0	221.0	23.5	36	<0.1	9.5	16.3	343	2.24	3.1	0.5	10.2	1.1	72	0.3	0.4	0.2	15	2.79
726597	Rock	2.63	40.1	606.8	6.8	35	0.2	7.9	25.2	292	5.90	1.5	1.6	11.7	4.3	145	<0.1	0.8	0.2	78	1.48
726598	Rock	3.43	11.3	553.4	7.2	36	0.3	6.3	15.6	258	5.22	2.1	1.5	18.6	4.3	91	0.1	0.2	0.4	104	1.28
726599	Rock	1.36	1.4	7.8	47.4	175	<0.1	2.2	13.8	2000	5.82	2.0	0.9	1.5	2.7	50	0.6	0.4	<0.1	73	1.28
726600	Rock	1.71	0.9	7.7	2.4	44	<0.1	11.6	5.6	416	1.57	9.9	0.1	131.3	1.0	20	0.4	0.4	0.5	18	0.67
726601	Rock	1.80	1.9	52.5	27.4	87	0.1	9.6	13.9	520	5.54	5.0	0.7	73.9	3.3	17	0.4	2.1	0.3	104	0.59
726602	Rock	2.23	8.2	49.2	3.6	5	<0.1	1.3	5.5	22	3.98	32.1	0.2	15.9	0.7	9	<0.1	1.4	0.3	5	0.01
726603	Rock	2.00	4.1	303.7	5.5	11	0.1	4.7	11.1	86	4.85	179.2	2.1	39.8	5.3	12	<0.1	6.0	0.2	10	0.35
726604	Rock	2.07	13.2	8.9	2.4	2	<0.1	2.0	1.1	17	0.59	67.2	0.1	0.6	1.2	8	<0.1	0.3	<0.1	6	0.02
726605	Rock	2.59	17.6	290.6	13.3	26	0.1	4.3	7.4	127	4.29	2.2	2.2	25.6	7.0	41	<0.1	<0.1	0.6	73	0.69
726606	Rock	2.15	0.7	52.5	12.4	44	<0.1	12.3	16.9	528	7.27	1.6	0.1	8.6	0.8	69	0.1	0.1	0.4	94	0.23
726607	Rock	1.84	0.6	186.4	12.8	31	0.2	7.6	14.9	233	6.98	11.1	0.2	272.9	0.6	64	<0.1	0.5	0.7	148	0.69
726608	Rock	1.70	3.9	217.4	20.4	114	0.6	4.4	16.5	648	4.54	18.6	5.9	3.4	16.1	37	0.6	9.7	2.9	45	0.61
726609	Rock	1.92	1.3	22.2	4.0	26	<0.1	6.9	12.3	401	3.59	5.8	0.1	5.1	0.9	38	0.1	0.5	0.2	20	0.15
726610	Rock	2.07	27.0	777.7	31.6	25	1.5	4.2	19.3	231	3.83	21.9	2.4	82.7	8.6	15	0.1	4.2	0.8	16	0.17

This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
 Report Date: August 04, 2008

Page: 2 of 3 Part 2

CERTIFICATE OF ANALYSIS

SMI08000616.1

Method	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se	
Unit	%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
MDL	0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5	
726581	Rock	0.036	10	14	0.83	167	0.004	2	2.35	0.065	0.27	2.4	<0.01	3.8	0.2	<0.05	6	<0.5
726582	Rock	0.217	4	6	1.02	14	0.004	1	3.07	0.006	0.03	1.7	0.06	5.0	0.3	7.71	9	16.3
726583	Rock	0.041	7	11	1.08	144	0.005	2	3.21	0.086	0.23	0.2	0.03	5.4	0.3	1.03	7	0.7
726584	Rock	0.097	7	8	0.77	108	0.004	2	2.93	0.085	0.19	<0.1	0.07	5.3	0.2	0.96	8	1.2
726585	Rock	0.174	9	15	1.00	27	0.004	1	3.65	0.083	0.05	0.2	0.21	11.9	0.9	2.88	13	5.5
726586	Rock	0.090	8	12	0.72	14	0.002	<1	2.66	0.040	0.06	<0.1	0.06	8.8	0.5	0.93	12	1.8
726587	Rock	0.071	8	4	2.99	78	0.001	2	0.83	0.037	0.11	0.1	0.02	3.1	0.4	1.51	2	<0.5
726588	Rock	0.165	9	6	1.50	66	0.001	2	2.69	0.129	0.14	0.1	0.06	6.7	0.4	2.26	9	<0.5
726589	Rock	0.093	1	12	1.14	27	0.002	2	2.71	0.056	0.15	0.4	0.66	7.6	0.5	7.89	9	14.5
726590	Rock	0.164	8	7	1.80	64	0.005	1	3.70	0.252	0.15	0.3	0.04	6.5	0.5	2.34	12	0.8
726591	Rock	0.233	2	3	0.20	114	0.003	1	0.98	0.037	0.35	0.2	0.06	1.9	0.3	1.41	2	0.9
726592	Rock	0.027	<1	4	0.29	24	0.001	<1	0.68	0.034	0.25	0.4	0.43	1.2	0.3	8.83	2	10.5
726593	Rock	0.079	2	4	0.54	23	<0.001	<1	0.73	0.076	0.19	0.5	0.14	1.3	0.2	4.54	2	4.5
726594	Rock	0.085	4	4	0.55	83	<0.001	<1	1.00	0.073	0.17	0.1	0.03	1.6	0.1	1.26	2	0.6
726595	Rock	0.032	4	5	0.29	100	0.003	2	1.50	0.041	0.67	0.2	0.01	3.0	0.7	1.39	3	1.6
726596	Rock	0.196	7	6	0.23	57	0.001	2	1.09	0.061	0.26	0.3	0.03	4.0	0.3	1.99	2	5.3
726597	Rock	0.172	16	7	1.59	30	0.043	2	2.52	0.141	0.36	0.1	0.03	5.8	0.6	3.61	8	4.1
726598	Rock	0.173	10	8	1.73	66	0.150	2	2.77	0.193	0.31	0.4	0.03	7.4	0.5	2.46	10	4.0
726599	Rock	0.177	12	3	1.17	78	0.119	2	3.14	0.061	0.10	0.4	<0.01	3.1	0.1	<0.05	11	<0.5
726600	Rock	0.035	4	11	0.51	92	0.002	1	1.63	0.057	0.22	<0.1	<0.01	2.0	0.2	<0.05	4	<0.5
726601	Rock	0.186	19	9	1.76	77	0.003	1	3.16	0.043	0.30	<0.1	0.01	7.4	0.6	0.41	13	<0.5
726602	Rock	0.024	3	2	0.06	130	<0.001	<1	0.69	0.046	0.29	0.2	0.22	0.8	0.2	0.94	1	4.3
726603	Rock	0.159	9	4	0.27	40	0.002	2	1.33	0.062	0.56	0.2	0.93	1.1	0.5	3.53	3	6.6
726604	Rock	0.010	2	2	0.01	151	<0.001	<1	0.64	0.031	0.30	<0.1	0.02	0.7	0.2	0.15	1	0.8
726605	Rock	0.130	12	10	1.04	42	0.129	3	1.50	0.086	0.17	0.5	0.06	4.3	0.1	2.54	7	5.1
726606	Rock	0.027	4	11	0.95	109	0.093	2	3.69	0.114	0.49	0.1	0.03	6.4	1.2	1.38	10	1.7
726607	Rock	0.076	2	15	1.10	78	0.003	1	3.14	0.216	0.21	0.1	0.03	7.5	0.6	2.10	12	1.2
726608	Rock	0.150	25	5	0.71	177	0.001	2	1.53	0.038	0.22	0.2	0.13	5.2	0.3	0.86	6	1.4
726609	Rock	0.025	4	2	0.22	87	0.002	1	1.86	0.100	0.16	<0.1	<0.01	2.6	0.3	0.87	4	<0.5
726610	Rock	0.172	7	3	0.06	84	<0.001	<1	0.83	0.044	0.21	0.2	0.06	2.5	0.4	1.12	2	4.3

This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
 Report Date: August 04, 2008

Page: 3 of 3 Part 1

CERTIFICATE OF ANALYSIS

SMI08000616.1

Method	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
Unit	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	
MDL	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	
726611	Rock	2.62	4.3	366.9	11.4	39	0.2	3.2	11.7	234	2.52	3.4	3.4	10.6	10.3	58	0.2	1.2	0.4	20	1.13
830900	Rock	1.90	1.2	5.9	10.1	76	<0.1	4.6	5.3	531	1.98	8.3	<0.1	0.7	0.3	19	0.1	1.6	<0.1	9	0.95
830901	Rock	1.56	1.1	4.5	66.5	123	<0.1	8.2	5.3	841	2.45	6.7	<0.1	<0.5	0.5	17	0.5	0.7	<0.1	16	0.47
830902	Rock	1.61	9.1	492.7	11.4	20	0.6	1.7	5.3	280	5.91	2.1	1.7	70.0	7.3	12	<0.1	0.2	0.8	20	0.21
830903	Rock	0.77	0.3	9.2	3.8	135	<0.1	10.2	10.9	1757	5.93	10.1	<0.1	<0.5	0.3	47	0.2	0.9	<0.1	116	1.60
830904	Rock	1.38	6.1	420.0	11.0	72	0.1	11.3	10.9	502	3.50	76.0	1.7	51.9	3.6	57	1.0	5.0	0.3	50	3.24
830905	Rock	2.05	1.2	16.0	21.2	77	<0.1	3.0	8.5	1208	2.82	1.8	2.9	2.4	6.3	108	0.3	0.1	<0.1	37	2.42
830906	Rock	1.41	50.3	3051	15.6	62	1.0	15.7	27.3	468	3.39	17.4	0.3	148.7	0.9	46	0.4	0.9	0.3	28	1.11
830907	Rock	1.27	0.6	4.6	4.6	44	<0.1	4.5	5.3	478	2.01	2.2	<0.1	5.6	0.5	30	<0.1	0.2	0.1	10	1.40
830908	Rock	1.87	2.0	11.7	10.4	53	<0.1	4.0	9.8	1104	3.15	11.5	0.6	2.2	1.9	52	<0.1	0.2	<0.1	49	2.23
830909	Rock	1.63	1.2	9.0	6.7	57	<0.1	4.9	4.6	352	1.92	6.0	0.1	1.8	0.5	13	<0.1	0.4	<0.1	14	0.87
830910	Rock	1.42	1.0	5.7	4.9	34	<0.1	7.9	3.8	254	0.81	11.8	0.1	<0.5	0.4	6	<0.1	0.4	<0.1	9	0.10
830911	Rock	1.70	1.1	4.5	19.4	89	<0.1	8.0	7.1	1728	3.53	7.6	0.4	<0.5	1.6	25	0.3	0.3	<0.1	35	0.93
830912	Rock	2.05	1.1	9.8	5.1	77	<0.1	8.1	8.3	844	3.03	7.6	0.1	<0.5	0.6	28	0.1	0.3	<0.1	28	3.69



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
Report Date: August 04, 2008

Page: 3 of 3 **Part** 2

CERTIFICATE OF ANALYSIS

SMI08000616.1

Method	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se	
Unit	%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
MDL	0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5	
726611	Rock	0.163	23	3	0.69	55	0.001	<1	1.29	0.082	0.21	0.2	0.05	1.7	0.3	1.96	4	2.0
830900	Rock	0.032	7	6	0.30	111	<0.001	1	0.90	0.051	0.19	<0.1	<0.01	2.1	<0.1	0.47	3	<0.5
830901	Rock	0.046	8	7	0.61	116	0.001	3	1.30	0.074	0.16	0.2	<0.01	2.3	<0.1	0.14	5	<0.5
830902	Rock	0.142	10	3	0.56	32	0.002	<1	1.79	0.017	0.47	0.1	0.01	1.2	0.4	2.16	6	1.7
830903	Rock	0.058	7	25	1.72	115	0.003	<1	3.55	0.054	0.12	<0.1	<0.01	8.2	<0.1	0.05	11	<0.5
830904	Rock	0.174	6	3	0.80	29	<0.001	2	1.13	0.009	0.11	<0.1	0.09	8.8	0.1	2.51	2	4.1
830905	Rock	0.140	24	4	0.73	434	0.015	2	1.65	0.051	0.29	0.2	<0.01	2.5	0.1	0.10	5	<0.5
830906	Rock	0.041	4	7	0.52	77	0.001	2	0.65	0.046	0.35	<0.1	0.19	6.2	0.2	1.27	2	3.5
830907	Rock	0.029	6	6	0.36	81	0.002	1	0.77	0.068	0.17	0.2	0.01	2.0	<0.1	0.72	3	<0.5
830908	Rock	0.110	19	5	0.90	102	0.007	1	1.90	0.061	0.17	0.2	0.02	2.0	<0.1	0.07	7	<0.5
830909	Rock	0.035	6	7	0.43	117	0.054	2	1.06	0.066	0.15	1.1	<0.01	2.2	<0.1	0.53	3	<0.5
830910	Rock	0.043	7	8	0.13	54	0.002	1	0.60	0.063	0.13	0.4	<0.01	1.4	<0.1	<0.05	2	<0.5
830911	Rock	0.059	10	11	0.55	161	0.004	3	1.61	0.038	0.18	0.2	<0.01	3.0	0.1	0.05	5	<0.5
830912	Rock	0.050	5	9	0.38	118	0.056	2	1.14	0.030	0.18	0.3	0.03	3.8	<0.1	1.02	3	<0.5

QUALITY CONTROL REPORT

SMI08000616.1

Method	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
Unit	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	
MDL	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	
Pulp Duplicates																					
726610	Rock	2.07	27.0	777.7	31.6	25	1.5	4.2	19.3	231	3.83	21.9	2.4	82.7	8.6	15	0.1	4.2	0.8	16	0.17
REP 726610	QC		27.4	784.6	31.9	26	1.5	3.7	19.7	238	3.86	22.7	2.5	82.5	8.9	15	0.1	4.1	0.8	16	0.17
Reference Materials																					
STD DS7	Standard		19.9	111.5	71.7	406	0.9	60.8	9.5	637	2.43	52.4	5.3	80.2	4.8	78	6.1	6.2	4.5	88	0.96
STD DS7	Standard		20.8	113.2	73.3	403	0.9	59.4	9.6	667	2.44	51.9	5.5	84.7	4.9	76	5.9	5.9	4.6	89	0.96
STD DS7	Standard		19.8	106.9	77.8	387	0.8	58.3	9.2	617	2.27	48.0	5.4	65.3	4.7	74	6.1	6.5	4.6	82	0.96
STD DS7	Standard		20.7	111.8	77.3	395	0.8	57.2	9.3	631	2.33	50.9	5.5	61.1	4.9	80	5.7	6.5	4.7	85	0.99
STD DS7 Expected			20.9	109	70.6	411	0.9	56	9.7	627	2.39	48.2	4.9	70	4.4	69	6.4	5.9	4.5	86	0.93
BLK	Blank		<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01
BLK	Blank		<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01
Prep Wash																					
G1	Prep Blank	<0.01	2.2	3.3	102.6	56	<0.1	12.1	4.9	592	2.03	<0.5	2.8	3.7	4.9	60	<0.1	0.4	0.2	41	0.56
G1	Prep Blank	<0.01	1.8	3.8	162.7	57	0.1	11.7	5.0	571	1.91	<0.5	2.8	3.5	5.0	55	<0.1	0.5	0.2	39	0.51



AcmeLabs ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
Report Date: August 04, 2008

Page: 1 of 1 **Part** 2

QUALITY CONTROL REPORT

SMI08000616.1

Method		1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte		P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
Unit		%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm
MDL		0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5
Pulp Duplicates																		
726610	Rock	0.172	7	3	0.06	84	<0.001	<1	0.83	0.044	0.21	0.2	0.06	2.5	0.4	1.12	2	4.3
REP 726610	QC	0.173	8	3	0.07	90	0.001	<1	0.85	0.049	0.23	0.2	0.08	2.5	0.4	1.13	2	3.9
Reference Materials																		
STD DS7	Standard	0.084	13	203	1.08	401	0.126	38	1.03	0.094	0.50	3.9	0.24	2.5	4.6	0.18	5	4.0
STD DS7	Standard	0.083	13	213	1.06	404	0.133	38	1.04	0.095	0.47	4.1	0.22	2.5	4.5	0.18	5	3.6
STD DS7	Standard	0.074	13	196	1.02	367	0.119	38	1.00	0.087	0.44	3.8	0.21	2.4	4.6	0.18	4	3.3
STD DS7	Standard	0.075	13	202	1.03	370	0.127	41	1.06	0.091	0.45	3.7	0.22	2.5	4.3	0.19	5	3.1
STD DS7 Expected		0.08	13	163	1.05	370	0.124	39	0.959	0.073	0.44	3.8	0.2	2.5	4.2	0.21	4.6	3.5
BLK	Blank	<0.001	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
BLK	Blank	<0.001	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
Prep Wash																		
G1	Prep Blank	0.077	9	20	0.69	252	0.140	1	1.07	0.076	0.58	2.6	<0.01	2.1	0.4	<0.05	5	<0.5
G1	Prep Blank	0.075	9	22	0.66	239	0.131	1	1.02	0.071	0.55	0.9	<0.01	1.8	0.5	<0.05	5	<0.5



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.

Vancouver BC V6C 1Z7 Canada

Submitted By:

Glen Garratt

Receiving Lab:

Canada-Smithers

Received:

July 18, 2008

Report Date:

August 06, 2008

Page:

1 of 2

CERTIFICATE OF ANALYSIS

SMI08000638.1

CLIENT JOB INFORMATION

Project: Zymo
Shipment ID: zy-st-08-03
P.O. Number
Number of Samples: 14

SAMPLE DISPOSAL

RTRN-PLP Return
DISP-RJT-SOIL Immediate Disposal of Soil Reject

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Mincord Exploration Consultants Ltd.
110 - 325 Howe St.
Vancouver BC V6C 1Z7
Canada

CC: Bob Johnston

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status
SS80	14	Dry at 60C sieve 100g to -80 mesh		
Dry at 60C	14	Dry at 60C		
1DX15	11	1:1:1 Aqua Regia digestion ICP-MS analysis	15	Completed

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only. All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
 Report Date: August 06, 2008

Page: 2 of 2 Part 1

CERTIFICATE OF ANALYSIS

SMI08000638.1

Method	Analyte	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
		Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	P
Unit		ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	%
MDL		0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	0.001
ZXB-08-012	Silt	2.6	64.6	30.0	159	0.2	12.2	16.9	1947	4.41	38.9	0.7	5.4	0.9	46	0.8	0.7	0.4	42	0.63	0.088
ZXB-08-013	Silt	2.9	58.4	26.4	139	0.2	16.2	14.8	2259	4.89	31.9	0.7	10.3	0.9	52	0.4	0.7	0.3	53	0.58	0.100
ZXR-08-022	Silt	4.3	102.6	71.8	220	0.4	24.0	21.6	3015	4.58	54.4	0.9	20.3	1.5	35	1.7	2.2	0.8	50	0.43	0.095
ZXR-08-023	Silt	6.3	129.4	81.0	215	0.5	19.7	24.0	2590	5.64	71.7	1.1	40.0	1.3	30	1.5	2.6	1.1	59	0.34	0.092
ZXR-08-024	Silt	9.8	200.3	120.9	267	0.6	23.2	35.3	4581	6.76	101.3	1.4	34.4	1.5	26	2.2	3.1	1.6	58	0.30	0.128
ZXR-08-025	Silt	5.9	121.1	73.4	206	0.5	19.0	23.6	3564	5.03	68.4	1.1	21.3	1.4	26	1.7	2.1	0.9	52	0.26	0.085
ZXR-08-026	Silt	4.7	97.6	70.6	171	0.4	12.6	23.1	2295	5.13	80.8	1.1	35.5	0.8	23	0.5	2.5	1.0	53	0.34	0.112
ZXR-08-027	Silt	9.4	47.9	53.0	204	0.2	14.0	22.7	7474	5.75	52.0	0.9	12.5	0.7	39	1.2	1.3	0.5	47	0.45	0.118
ZXR-08-028	Silt	5.5	140.1	96.1	252	0.4	27.5	24.5	2246	5.54	75.1	1.1	18.9	1.9	36	1.3	3.0	1.1	58	0.46	0.097
ZXR-08-029	Silt	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.
ZXR-08-030	Silt	4.3	74.0	37.0	175	0.2	23.4	25.1	5319	5.12	29.5	0.9	7.7	0.9	47	0.9	1.4	0.4	52	0.50	0.104
ZXR-08-031	Silt	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.
ZXR-08-032	Silt	1.4	46.7	14.1	98	<0.1	16.9	18.1	1460	4.15	16.0	0.3	4.0	0.6	38	0.3	0.8	0.2	44	0.61	0.068
ZXR-08-033	Silt	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**

110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo

Report Date: August 06, 2008

Page: 2 of 2 Part 2

CERTIFICATE OF ANALYSIS

SMI08000638.1

Method	Analyte	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
		La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
Unit		ppm	ppm	%	ppm	%	ppm	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
MDL		1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.05	1	0.5	
ZXB-08-012	Silt	10	7	0.44	189	0.001	<1	1.75	0.008	0.04	<0.1	0.08	4.8	0.1	<0.05	4	1.1
ZXB-08-013	Silt	8	10	0.35	190	0.004	<1	1.54	0.008	0.05	<0.1	0.08	3.5	0.2	<0.05	5	1.0
ZXR-08-022	Silt	11	14	0.34	233	0.014	2	1.22	0.014	0.08	0.1	0.10	4.9	0.2	0.33	3	1.6
ZXR-08-023	Silt	11	13	0.30	184	0.012	1	1.28	0.009	0.06	<0.1	0.13	4.5	0.2	0.44	3	1.8
ZXR-08-024	Silt	16	14	0.30	211	0.013	2	1.78	0.007	0.07	0.1	0.16	5.3	0.3	0.10	4	3.2
ZXR-08-025	Silt	12	11	0.26	172	0.009	<1	1.38	0.006	0.05	<0.1	0.13	4.0	0.2	0.10	4	1.9
ZXR-08-026	Silt	11	8	0.23	95	0.007	<1	1.97	0.006	0.04	<0.1	0.12	3.2	0.2	0.07	5	1.4
ZXR-08-027	Silt	8	6	0.23	289	0.006	1	1.18	0.006	0.05	0.1	0.07	2.5	0.4	0.07	4	0.9
ZXR-08-028	Silt	11	17	0.39	186	0.016	<1	1.28	0.017	0.08	<0.1	0.11	5.2	0.2	0.61	4	2.1
ZXR-08-029	Silt	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.
ZXR-08-030	Silt	9	11	0.32	225	0.011	1	1.72	0.010	0.07	0.1	0.10	4.3	0.2	0.13	5	1.1
ZXR-08-031	Silt	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.
ZXR-08-032	Silt	6	10	0.47	146	0.002	<1	1.84	0.009	0.04	<0.1	0.11	4.9	<0.1	0.08	5	0.7
ZXR-08-033	Silt	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.

QUALITY CONTROL REPORT

SMI08000638.1

Method	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
Analyte	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	P	
Unit	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	%	
MDL	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	0.001	
Pulp Duplicates																					
ZXB-08-013	Silt	2.9	58.4	26.4	139	0.2	16.2	14.8	2259	4.89	31.9	0.7	10.3	0.9	52	0.4	0.7	0.3	53	0.58	0.100
REP ZXB-08-013	QC	3.1	60.0	26.5	141	0.2	14.7	15.3	2397	5.02	32.8	0.7	5.5	0.9	54	0.5	0.7	0.3	54	0.61	0.104
Reference Materials																					
STD DS7	Standard	20.0	107.9	74.1	383	0.8	54.3	9.3	602	2.30	47.2	5.2	59.0	4.6	67	5.9	5.8	4.3	84	0.90	0.067
STD DS7	Standard	19.2	107.9	72.8	394	0.9	57.6	9.4	627	2.36	49.1	4.6	66.0	3.7	64	6.4	6.1	4.3	86	0.89	0.073
STD DS7 Expected		20.9	109	70.6	411	0.9	56	9.7	627	2.39	48.2	4.9	70	4.4	69	6.4	5.9	4.5	86	0.93	0.08
BLK	Blank	<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01	<0.001
BLK	Blank	<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01	<0.001

QUALITY CONTROL REPORT

SMI08000638.1

Method	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se	
Unit	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
MDL	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5	
Pulp Duplicates																	
ZXB-08-013	Silt	8	10	0.35	190	0.004	<1	1.54	0.008	0.05	<0.1	0.08	3.5	0.2	<0.05	5	1.0
REP ZXB-08-013	QC	8	11	0.36	193	0.004	<1	1.57	0.009	0.05	<0.1	0.08	3.8	0.2	0.05	5	1.2
Reference Materials																	
STD DS7	Standard	12	202	0.97	359	0.123	33	0.96	0.082	0.42	3.8	0.19	2.3	4.1	0.18	5	4.2
STD DS7	Standard	11	204	1.04	395	0.109	38	0.97	0.092	0.46	4.2	0.22	2.1	4.9	0.19	4	3.2
STD DS7 Expected		13	163	1.05	370	0.124	39	0.959	0.073	0.44	3.8	0.2	2.5	4.2	0.21	5	3.5
BLK	Blank	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
BLK	Blank	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.

Vancouver BC V6C 1Z7 Canada

Submitted By:

Glen Garratt

Receiving Lab:

Canada-Smithers

Received:

July 18, 2008

Report Date:

August 01, 2008

Page:

1 of 3

CERTIFICATE OF ANALYSIS

SMI08000639.1

CLIENT JOB INFORMATION

Project: Zymo
Shipment ID: zy-rk-08-06
P.O. Number
Number of Samples: 51

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
DISP-RJT Dispose of Reject After 90 days

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Mincord Exploration Consultants Ltd.
110 - 325 Howe St.
Vancouver BC V6C 1Z7
Canada

CC: Bob Johnston

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status
R150	51	Crush, split and pulverize rock to 200 mesh		
1DX15	51	1:1:1 Aqua Regia digestion ICP-MS analysis	15	Completed

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only. All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**

110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo

Report Date: August 01, 2008

Page: 2 of 3 Part 1

CERTIFICATE OF ANALYSIS

SMI08000639.1

Method	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
Unit	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	
MDL	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	
726612	Rock	0.33	9.2	112.8	696.1	259	4.5	1.4	2.7	73	2.88	7.6	2.0	166.2	7.2	8	1.2	0.2	8.0	8	0.07
726613	Rock	1.10	0.7	40.2	4.7	65	<0.1	11.3	16.2	519	3.64	2.2	<0.1	<0.5	0.4	39	<0.1	<0.1	0.1	32	0.46
726614	Rock	1.97	1.1	13.4	7.1	23	<0.1	4.5	6.0	156	2.49	99.9	<0.1	3.3	0.6	12	<0.1	3.7	0.3	12	0.06
726615	Rock	2.15	7.2	1060	11.8	70	0.4	4.1	13.3	361	3.72	3.5	1.4	68.4	4.9	439	0.3	0.4	0.3	57	0.74
726616	Rock	2.64	4.0	189.0	6.0	39	<0.1	4.2	5.0	265	3.84	4.7	1.6	9.6	4.8	118	<0.1	<0.1	<0.1	98	1.32
726617	Rock	2.89	14.4	373.8	12.6	38	0.1	2.8	11.1	325	2.36	1.2	4.7	40.5	13.7	61	<0.1	<0.1	0.1	37	0.36
726618	Rock	2.11	11.1	464.0	56.5	70	0.3	4.3	26.2	782	4.96	8.3	1.9	41.0	4.0	34	<0.1	0.2	0.3	53	0.29
726619	Rock	2.76	5.0	130.5	12.5	28	0.2	2.2	2.1	288	4.32	6.2	0.1	22.5	1.1	20	<0.1	0.2	0.4	31	0.03
726620	Rock	2.37	6.2	688.0	14.0	37	0.3	10.1	43.9	266	8.47	2.3	0.2	46.6	0.8	114	0.2	0.3	0.5	48	1.50
726621	Rock	2.04	1.0	286.8	10.0	14	0.1	7.2	35.8	82	9.28	4.4	0.2	37.3	0.4	15	0.1	0.1	0.6	12	0.29
726622	Rock	1.93	4.8	115.8	5.5	35	<0.1	5.9	16.2	242	3.29	6.9	0.9	11.9	2.1	44	<0.1	0.1	0.2	29	1.22
726623	Rock	2.63	20.6	73.2	20.4	31	0.1	19.0	23.7	34	6.19	3.5	0.7	10.7	0.7	21	0.2	<0.1	0.6	6	0.20
726624	Rock	2.63	15.2	221.1	8.9	8	0.1	1.9	9.5	286	5.57	3.4	2.2	44.8	6.4	10	<0.1	0.3	0.3	4	0.08
726625	Rock	0.80	1.8	49.2	4.5	38	<0.1	5.5	4.5	220	2.29	<0.5	0.4	3.8	1.6	25	0.2	<0.1	0.4	9	0.05
726626	Rock	2.71	84.2	1794	10.3	30	0.8	10.4	141.7	283	7.90	7.1	1.1	63.7	4.2	25	0.2	0.4	1.4	8	1.93
726627	Rock	1.97	29.5	940.7	6.3	41	0.3	8.4	20.6	250	4.87	2.2	1.1	39.9	4.5	90	0.1	<0.1	0.2	114	1.05
726628	Rock	4.35	50.9	1102	166.4	219	0.6	7.6	22.0	1377	4.55	47.7	1.1	41.4	4.0	45	1.1	1.3	0.2	61	1.34
726629	Rock	2.79	27.9	1252	41.2	88	0.6	15.5	23.3	766	2.54	74.9	0.2	51.8	0.9	51	0.6	3.3	0.3	12	2.12
726630	Rock	3.15	7.7	4156	10.6	41	2.3	3.8	10.1	238	8.21	6.5	1.1	699.0	6.4	10	<0.1	1.4	0.4	85	0.05
726631	Rock	2.65	10.3	2827	11.8	53	1.1	7.2	8.5	284	3.59	1.7	0.3	349.0	2.2	14	0.1	<0.1	0.3	68	0.25
726632	Rock	2.03	9.2	1213	11.3	72	0.4	8.0	25.3	550	4.43	2.7	1.2	96.3	7.2	65	0.3	0.1	0.1	68	0.78
726633	Rock	2.22	10.2	505.3	12.1	43	0.2	4.6	6.5	357	1.95	1.8	7.3	25.1	12.9	457	0.2	0.3	0.1	48	1.96
726634	Rock	1.93	49.8	123.7	6.6	12	<0.1	1.8	2.3	36	3.65	8.0	<0.1	21.6	0.9	18	<0.1	0.2	0.4	9	0.03
726635	Rock	2.09	3.6	834.7	15.2	79	0.5	12.0	20.0	336	8.93	17.3	0.2	62.1	0.9	5	<0.1	0.4	0.7	64	0.09
726636	Rock	2.86	4.9	4909	24.4	60	2.2	39.7	151.1	242	21.37	51.1	0.3	164.4	0.4	3	0.1	0.3	1.8	63	0.36
726637	Rock	3.23	3.8	390.7	8.9	46	0.2	10.2	122.8	1343	24.03	1.1	0.2	67.1	0.5	13	<0.1	<0.1	2.7	116	0.35
830913	Rock	1.85	1.1	26.4	40.2	47	0.4	28.1	12.3	38	3.81	13.8	0.2	24.9	0.4	8	0.2	0.4	1.7	5	0.03
830914	Rock	1.63	1.3	9.5	23.1	75	0.1	6.6	15.7	1188	5.45	5.7	<0.1	<0.5	0.4	86	0.2	2.2	<0.1	103	2.28
830915	Rock	1.94	5.8	12.0	11.7	99	0.1	9.5	13.1	1541	5.34	44.2	0.1	<0.5	0.5	213	0.2	1.4	<0.1	58	7.93
830916	Rock	0.57	0.7	31.2	4.8	50	<0.1	3.7	8.5	235	2.74	2.6	3.0	108.4	8.9	49	0.2	0.2	0.9	47	0.79



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**

110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo

Report Date: August 01, 2008

Page: 2 of 3 Part 2

CERTIFICATE OF ANALYSIS

SMI08000639.1

Method	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se	
Unit	%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
MDL	0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.01	0.05	1	0.5	
726612	Rock	0.118	12	7	0.10	143	0.002	<1	0.51	0.009	0.38	0.2	<0.01	0.6	0.5	0.97	2	4.0
726613	Rock	0.019	25	11	0.55	146	0.002	1	2.03	0.024	0.17	<0.1	<0.01	3.9	<0.1	<0.05	6	<0.5
726614	Rock	0.024	<1	3	0.19	104	<0.001	2	1.47	0.033	0.18	<0.1	0.06	2.4	0.3	0.10	3	<0.5
726615	Rock	0.211	27	2	0.70	231	0.024	1	1.45	0.071	0.24	<0.1	0.15	4.2	0.3	0.58	6	2.3
726616	Rock	0.180	14	8	1.44	123	0.239	2	2.43	0.212	0.30	<0.1	0.03	7.3	0.4	0.08	8	0.9
726617	Rock	0.125	33	4	0.66	167	0.021	1	1.24	0.070	0.28	<0.1	0.01	2.1	0.3	0.66	4	3.3
726618	Rock	0.167	17	5	1.16	521	0.012	2	2.24	0.023	0.26	<0.1	0.01	4.8	0.4	0.23	7	3.1
726619	Rock	0.058	5	5	0.55	415	0.003	1	1.73	0.069	0.43	<0.1	0.01	3.0	0.6	0.24	5	3.8
726620	Rock	0.141	7	10	0.44	28	0.007	2	2.21	0.214	0.34	<0.1	0.01	4.6	0.6	7.07	5	11.3
726621	Rock	0.061	2	4	0.17	24	0.002	1	0.72	0.042	0.28	<0.1	0.08	2.4	0.4	8.81	2	6.5
726622	Rock	0.173	7	3	0.39	64	0.001	3	1.05	0.021	0.16	<0.1	0.06	5.1	0.6	2.14	2	3.1
726623	Rock	0.094	5	6	0.07	11	0.001	1	0.62	0.041	0.25	<0.1	0.17	1.3	0.3	6.05	<1	12.2
726624	Rock	0.153	12	2	0.15	186	0.002	1	1.10	0.041	0.30	<0.1	0.06	1.5	0.3	0.69	1	7.9
726625	Rock	0.018	4	2	0.18	167	<0.001	1	1.26	0.052	0.24	<0.1	<0.01	1.3	0.3	0.32	3	<0.5
726626	Rock	0.089	7	4	0.63	17	0.001	2	0.33	0.019	0.24	<0.1	0.18	1.8	0.3	7.35	<1	7.8
726627	Rock	0.162	11	10	1.76	104	0.255	2	2.60	0.176	0.12	0.1	0.08	8.5	0.2	1.25	10	2.2
726628	Rock	0.152	15	6	0.79	244	0.012	2	1.52	0.066	0.23	<0.1	0.48	7.9	0.4	0.22	4	2.9
726629	Rock	0.031	3	2	0.52	123	<0.001	2	0.57	0.028	0.32	<0.1	0.18	4.6	0.3	0.98	1	2.3
726630	Rock	0.024	3	10	0.04	100	0.002	1	0.18	0.013	0.15	<0.1	0.30	1.2	<0.1	0.45	3	5.2
726631	Rock	0.064	6	16	0.27	211	0.009	1	0.51	0.045	0.22	<0.1	0.38	5.8	0.1	0.31	4	2.6
726632	Rock	0.175	13	8	1.34	107	0.094	1	2.10	0.145	0.21	<0.1	0.03	4.4	0.2	0.78	7	3.3
726633	Rock	0.109	38	6	0.58	426	0.003	2	1.05	0.038	0.21	<0.1	0.08	1.9	0.2	0.33	4	0.8
726634	Rock	0.084	3	2	0.06	155	<0.001	1	0.58	0.043	0.26	<0.1	0.05	1.2	0.3	0.16	1	4.6
726635	Rock	0.075	4	8	0.65	91	0.005	1	2.70	0.025	0.29	<0.1	0.06	4.4	0.4	1.65	7	4.3
726636	Rock	0.255	4	9	0.41	7	0.005	1	1.63	0.007	0.08	<0.1	0.10	5.7	0.1	>10	8	29.3
726637	Rock	0.153	4	8	0.87	19	0.009	<1	4.34	0.024	0.06	<0.1	0.04	7.7	0.3	8.26	12	7.8
830913	Rock	0.011	<1	11	0.02	29	<0.001	2	0.22	0.010	0.14	<0.1	0.10	0.5	0.2	3.73	<1	4.4
830914	Rock	0.106	6	13	1.16	59	0.004	1	2.25	0.063	0.09	<0.1	<0.01	7.7	<0.1	1.94	11	<0.5
830915	Rock	0.212	7	13	1.17	79	0.003	1	1.93	0.024	0.12	0.1	0.03	5.9	<0.1	2.43	5	<0.5
830916	Rock	0.143	40	3	0.82	58	0.002	1	1.08	0.074	0.14	<0.1	0.04	3.0	0.2	2.09	5	1.2



AcmeLabs ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
Report Date: August 01, 2008

Page: 3 of 3 **Part** 1

CERTIFICATE OF ANALYSIS

SMI08000639.1

Method	Analyte	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca
Unit	MDL	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	ppm	
		0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01
830917	Rock	0.63	0.9	649.5	1.9	10	0.1	4.5	10.1	40	3.55	1.8	0.2	140.2	1.2	6	<0.1	0.5	0.2	8	0.10
830918	Rock	0.34	0.8	154.1	2.3	7	<0.1	4.6	10.9	37	3.99	1.9	0.2	65.5	0.9	5	<0.1	0.3	0.3	8	0.04
830919	Rock	1.03	1.3	26.4	18.9	17	0.3	38.8	9.0	322	3.62	20.7	<0.1	18.2	0.5	9	0.1	0.4	0.9	4	0.07
830920	Rock	0.86	0.3	918.3	51.6	324	1.1	22.1	31.6	1491	8.12	104.3	0.3	49.1	2.1	20	1.3	1.4	6.5	86	0.68
830921	Rock	1.17	1.3	2675	10.5	45	0.8	4.1	8.3	270	3.86	2.5	1.9	227.8	12.9	323	0.2	0.4	0.2	62	0.53
830922	Rock	0.19	1.7	49.3	9.1	112	<0.1	5.1	16.9	1186	4.08	10.2	1.3	29.8	3.5	336	0.5	0.7	<0.1	54	5.06
830923	Rock	0.78	1.4	1146	20.7	47	0.5	12.4	120.3	528	23.48	6.5	<0.1	130.9	0.1	18	<0.1	0.5	4.9	36	1.63
830924	Rock	0.50	1.7	82.7	5.1	28	<0.1	4.7	5.0	468	2.36	1.0	0.6	1.0	0.8	61	0.1	<0.1	0.2	71	1.47
830925	Rock	1.62	1.5	16.4	6.6	56	<0.1	7.8	9.0	768	2.61	1.4	2.2	<0.5	5.9	111	0.1	0.1	<0.1	55	1.21
830926	Rock	1.59	2.0	21.8	6.7	77	<0.1	12.9	13.5	863	4.06	17.4	0.6	<0.5	1.3	19	0.1	0.6	<0.1	109	0.57
830927	Rock	1.78	0.8	21.8	8.7	81	<0.1	10.9	11.7	1322	3.02	7.4	0.3	<0.5	0.8	23	<0.1	0.4	0.3	86	1.02
830928	Rock	1.49	4.1	4.1	131.9	22	1.0	1.3	0.3	95	1.62	36.5	0.2	51.4	1.7	7	0.1	1.2	1.9	6	0.02
830929	Rock	2.86	1.6	298.2	58.1	57	1.6	42.8	10.5	201	2.75	27.8	0.6	98.5	4.0	14	0.3	1.4	2.3	20	0.31
830930	Rock	0.48	1.5	93.7	29.6	111	0.3	8.0	10.6	190	2.88	8.6	3.7	21.5	7.5	26	0.8	<0.1	2.9	23	0.31
830931	Rock	1.26	0.6	29.5	3.1	75	<0.1	7.6	16.5	1018	4.42	6.0	0.3	<0.5	1.3	33	<0.1	1.0	<0.1	100	1.17
830932	Rock	1.01	1.5	9.9	250.9	12	1.5	8.8	3.3	52	2.45	47.9	0.1	8.2	1.8	7	<0.1	0.7	3.4	4	<0.01
830933	Rock	1.54	0.6	18.9	1.4	54	<0.1	5.0	11.0	899	3.54	5.4	0.2	<0.5	1.0	112	<0.1	0.9	<0.1	62	2.64
830934	Rock	1.43	1.0	7.0	1.8	18	<0.1	0.7	2.2	1753	1.21	3.2	<0.1	<0.5	0.2	416	<0.1	0.3	<0.1	6	20.98
830935	Rock	0.50	3.4	19.6	5.6	94	<0.1	9.2	12.7	768	6.10	4.6	0.5	<0.5	0.7	54	<0.1	0.2	<0.1	88	5.96
830936	Rock	1.26	0.7	23.2	5.1	71	<0.1	18.8	14.6	617	2.50	3.1	0.3	<0.5	0.9	41	<0.1	0.1	<0.1	69	2.49
830937	Rock	1.55	0.8	18.8	7.0	119	<0.1	13.1	19.0	1029	6.69	21.3	0.3	3.3	0.6	28	0.1	0.4	0.1	139	1.45



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
Report Date: August 01, 2008

Page: 3 of 3 **Part** 2

CERTIFICATE OF ANALYSIS

SMI08000639.1

Method	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se	
Unit	%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
MDL	0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5	
830917	Rock	0.030	2	2	0.21	24	0.003	<1	0.71	0.020	0.28	<0.1	0.03	0.9	0.3	3.42	1	2.7
830918	Rock	0.024	2	2	0.24	19	0.003	<1	0.78	0.023	0.30	<0.1	0.03	1.1	0.3	3.67	1	3.1
830919	Rock	0.026	1	15	<0.01	25	<0.001	<1	0.14	0.005	0.07	<0.1	0.03	0.4	0.1	3.63	<1	1.2
830920	Rock	0.189	7	15	1.90	16	0.002	2	0.81	0.017	0.20	<0.1	0.02	7.1	0.5	6.35	2	2.6
830921	Rock	0.118	16	11	0.61	310	0.019	1	0.85	0.047	0.21	<0.1	0.26	3.4	0.1	0.40	6	2.5
830922	Rock	0.157	18	2	1.00	150	<0.001	1	0.90	0.029	0.14	<0.1	0.02	6.2	<0.1	0.93	2	1.3
830923	Rock	0.692	3	10	0.87	18	0.005	<1	3.04	0.047	0.05	<0.1	1.27	4.6	0.3	>10	8	11.5
830924	Rock	0.113	4	9	0.81	37	0.136	2	1.72	0.170	0.03	0.1	<0.01	4.2	<0.1	0.52	6	<0.5
830925	Rock	0.142	22	11	0.72	111	0.090	2	1.54	0.084	0.15	0.3	<0.01	2.8	<0.1	<0.05	7	<0.5
830926	Rock	0.083	8	29	1.17	124	0.304	1	1.83	0.070	0.05	0.3	0.04	10.6	<0.1	<0.05	11	<0.5
830927	Rock	0.065	7	23	0.78	61	0.192	<1	1.40	0.064	0.05	0.1	0.03	8.1	<0.1	<0.05	9	<0.5
830928	Rock	0.026	5	15	0.03	137	0.001	<1	0.36	0.014	0.39	<0.1	0.35	0.4	0.3	0.28	1	1.1
830929	Rock	0.056	8	28	0.28	84	0.001	2	0.62	0.019	0.25	<0.1	0.24	2.4	0.4	1.48	2	1.1
830930	Rock	0.137	8	5	0.06	41	0.001	<1	0.65	0.029	0.20	<0.1	0.02	2.5	0.3	2.37	1	1.0
830931	Rock	0.094	16	11	1.26	83	0.003	2	2.07	0.055	0.09	<0.1	0.01	7.2	<0.1	0.07	10	<0.5
830932	Rock	0.035	4	8	<0.01	64	<0.001	<1	0.21	0.006	0.17	<0.1	0.08	0.9	0.6	1.49	<1	5.7
830933	Rock	0.076	10	7	1.15	41	0.003	1	1.32	0.063	0.07	<0.1	<0.01	4.1	<0.1	0.19	5	<0.5
830934	Rock	0.019	16	4	0.35	33	<0.001	1	0.28	0.006	0.07	<0.1	<0.01	1.6	<0.1	<0.05	<1	<0.5
830935	Rock	0.119	7	18	1.02	21	0.218	8	3.14	0.031	0.02	0.4	<0.01	6.6	<0.1	2.78	9	<0.5
830936	Rock	0.094	11	34	1.03	109	0.105	<1	1.95	0.046	0.07	<0.1	0.02	6.1	<0.1	<0.05	7	<0.5
830937	Rock	0.050	5	30	1.75	76	0.301	5	3.45	0.052	0.05	0.1	0.03	10.7	<0.1	0.27	13	<0.5

QUALITY CONTROL REPORT

SMI08000639.1

Method	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
Unit	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	
MDL	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	
Pulp Duplicates																					
830925	Rock	1.62	1.5	16.4	6.6	56	<0.1	7.8	9.0	768	2.61	1.4	2.2	<0.5	5.9	111	0.1	0.1	<0.1	55	1.21
REP 830925	QC		1.6	16.8	7.0	57	<0.1	7.0	9.0	770	2.63	1.2	2.3	<0.5	5.6	111	<0.1	0.1	<0.1	57	1.22
Reference Materials																					
STD DS7	Standard		20.7	128.7	69.8	432	0.9	58.9	9.9	654	2.44	52.4	5.2	83.2	4.6	77	6.7	6.3	4.6	91	0.98
STD DS7	Standard		22.6	123.1	71.0	416	0.8	58.6	10.1	654	2.41	51.8	5.3	61.6	4.6	79	6.8	6.2	4.7	91	0.99
STD DS7	Standard		18.3	106.9	64.7	385	0.8	52.3	9.7	613	2.26	46.6	4.9	59.6	4.1	66	5.8	6.0	4.2	81	0.91
STD DS7	Standard		20.6	112.4	63.3	404	0.8	52.8	9.7	642	2.43	53.5	4.7	62.4	4.2	79	6.1	6.4	4.4	81	0.95
STD DS7	Standard		20.5	113.9	70.0	406	0.8	58.6	9.6	620	2.38	51.6	5.0	64.3	4.5	77	6.0	6.1	4.6	89	0.96
STD DS7	Standard		20.9	109.2	73.2	411	0.8	56.8	9.7	620	2.36	51.4	5.3	59.3	4.7	78	6.3	6.0	4.7	84	0.95
STD DS7 Expected			20.9	109	70.6	411	0.9	56	9.7	627	2.39	48.2	4.9	70	4.4	69	6.4	5.9	4.5	86	0.93
BLK	Blank		<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01
BLK	Blank		<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01
BLK	Blank		<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01
Prep Wash																					
G1	Prep Blank	<0.01	0.7	2.2	11.2	47	<0.1	4.4	4.3	546	1.83	<0.5	2.2	0.8	3.9	60	<0.1	<0.1	<0.1	35	0.50
G1	Prep Blank	<0.01	0.5	3.7	5.3	48	<0.1	5.2	4.9	598	1.98	0.7	2.5	<0.5	4.1	71	<0.1	<0.1	<0.1	38	0.57

QUALITY CONTROL REPORT

SMI08000639.1

Method		1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
Analyte		P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se	
Unit		%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
MDL		0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5	
Pulp Duplicates																			
830925	Rock	0.142	22	11	0.72	111	0.090	2	1.54	0.084	0.15	0.3	<0.01	2.8	<0.1	<0.05	7	<0.5	
REP 830925	QC	0.137	23	11	0.72	115	0.094	1	1.57	0.087	0.14	0.3	<0.01	2.8	<0.1	<0.05	7	<0.5	
Reference Materials																			
STD DS7	Standard	0.078	14	204	1.07	392	0.142	37	1.05	0.093	0.46	4.2	0.21	2.6	4.6	0.20	5	4.0	
STD DS7	Standard	0.077	14	209	1.07	397	0.147	36	1.06	0.090	0.46	4.3	0.20	2.8	4.4	0.20	5	4.2	
STD DS7	Standard	0.067	12	192	1.01	345	0.134	35	0.98	0.082	0.42	4.0	0.19	2.2	4.2	0.17	5	3.5	
STD DS7	Standard	0.080	14	199	1.03	400	0.143	38	1.05	0.092	0.46	4.0	0.19	2.4	4.0	0.18	5	3.9	
STD DS7	Standard	0.075	13	197	1.04	392	0.140	41	1.03	0.087	0.48	3.8	0.20	2.5	4.2	0.19	5	3.8	
STD DS7	Standard	0.070	13	203	1.05	383	0.139	40	1.02	0.086	0.45	3.9	0.21	2.4	4.4	0.20	5	3.9	
STD DS7 Expected		0.08	13	163	1.05	370	0.124	39	0.959	0.073	0.44	3.8	0.2	2.5	4.2	0.21	4.6	3.5	
BLK	Blank	<0.001	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5	
BLK	Blank	<0.001	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5	
BLK	Blank	<0.001	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5	
Prep Wash																			
G1	Prep Blank	0.074	8	24	0.56	213	0.138	2	1.04	0.068	0.52	0.1	<0.01	1.9	0.4	<0.05	5	<0.5	
G1	Prep Blank	0.077	9	16	0.59	217	0.158	1	1.29	0.096	0.53	<0.1	<0.01	2.2	0.4	<0.05	5	<0.5	



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.

Vancouver BC V6C 1Z7 Canada

Submitted By:

Glen Garratt

Receiving Lab:

Canada-Smithers

Received:

July 21, 2008

Report Date:

August 01, 2008

Page:

1 of 3

CERTIFICATE OF ANALYSIS

SMI08000643.1

CLIENT JOB INFORMATION

Project: Zymo
Shipment ID: zy-rk-08-07
P.O. Number
Number of Samples: 36

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
DISP-RJT Dispose of Reject After 90 days

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Mincord Exploration Consultants Ltd.
110 - 325 Howe St.
Vancouver BC V6C 1Z7
Canada

CC: Bob Johnston

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status
R150	36	Crush, split and pulverize rock to 200 mesh		
1DX15	36	1:1:1 Aqua Regia digestion ICP-MS analysis	15	Completed

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only. All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**

110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo

Report Date: August 01, 2008

Page: 2 of 3 Part 1

CERTIFICATE OF ANALYSIS

SMI08000643.1

Method	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
Unit	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	
MDL	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	
726638	Rock	1.86	0.7	27.8	8.9	62	<0.1	8.3	6.6	780	5.76	0.9	<0.1	8.6	0.5	60	<0.1	0.3	0.3	78	1.72
726639	Rock	1.94	35.5	96.8	16.5	75	0.3	9.6	28.1	830	9.02	37.3	0.4	273.8	1.4	15	0.1	3.1	4.2	79	1.01
726640	Rock	1.41	1.8	8.1	117.4	76	0.1	11.0	1.6	33	1.38	41.0	<0.1	5.1	0.9	17	0.2	0.6	1.2	9	0.02
726641	Rock	1.50	26.4	831.2	5.7	37	0.3	4.7	13.6	221	3.10	2.8	1.7	28.8	7.8	397	0.1	0.3	0.2	72	0.72
726642	Rock	1.84	14.7	319.5	7.5	31	<0.1	4.9	7.8	392	1.78	4.2	0.1	16.8	0.7	55	0.2	0.3	0.1	32	0.85
726643	Rock	1.94	62.9	1513	6.9	33	0.3	8.3	20.4	325	2.41	6.6	0.6	60.2	2.1	50	0.2	3.5	0.1	17	2.75
726644	Rock	1.77	2.9	328.3	4.9	40	0.1	10.3	24.5	309	4.39	1.1	0.6	27.2	1.2	80	0.1	<0.1	0.2	108	1.10
726645	Rock	2.14	10.7	126.8	3.4	13	<0.1	2.4	7.8	107	1.12	1.1	0.2	12.4	0.5	18	<0.1	<0.1	0.1	10	0.16
726646	Rock	2.27	9.7	375.0	4.5	22	0.3	3.3	9.4	164	3.15	2.4	1.2	22.8	6.1	23	<0.1	0.2	0.8	40	0.43
726647	Rock	1.91	2.6	121.0	3.6	14	<0.1	6.8	14.5	190	4.05	4.6	0.1	10.2	0.6	14	<0.1	1.0	0.8	40	0.42
726648	Rock	1.77	2.8	175.1	6.9	13	<0.1	5.8	10.7	465	5.42	2.7	<0.1	10.0	0.6	13	<0.1	1.4	0.3	44	0.21
726649	Rock	2.30	5.8	519.6	7.4	20	0.3	4.2	5.6	119	4.25	2.3	0.7	99.0	3.9	26	<0.1	<0.1	0.1	100	0.28
830938	Rock	1.81	2.0	12.8	34.3	73	0.3	4.3	8.1	809	3.28	11.9	3.7	19.5	6.4	21	0.4	0.1	5.3	15	0.66
830939	Rock	1.67	0.5	77.1	7.9	56	<0.1	5.0	19.7	977	4.79	15.3	1.0	2.0	1.6	457	<0.1	0.8	<0.1	191	2.30
830940	Rock	1.38	1.6	18.3	8.6	47	1.0	1.7	1.9	79	1.50	13.1	0.2	1.0	0.3	16	0.2	8.1	<0.1	4	<0.01
830941	Rock	1.45	3.1	37.0	7.6	82	<0.1	7.3	9.5	918	2.69	1.9	1.5	3.4	3.0	76	0.1	0.1	<0.1	58	1.59
830942	Rock	1.61	5.4	145.1	35.5	308	0.3	6.0	10.7	1770	3.54	14.8	2.7	11.6	4.7	37	2.6	0.7	1.1	54	2.01
830943	Rock	1.49	21.6	779.3	17.8	173	0.9	4.9	10.1	2257	3.42	11.7	1.8	23.5	3.4	202	1.2	0.5	<0.1	76	1.33
830944	Rock	1.64	6.1	110.6	63.2	299	0.3	5.5	9.2	1405	3.46	9.2	1.6	8.6	4.9	22	1.5	1.0	0.4	63	0.41
830945	Rock	1.11	1.0	43.7	86.1	72	1.0	30.5	7.0	147	2.21	8.3	0.5	20.7	2.7	5	0.1	0.4	4.2	9	0.04
830946	Rock	1.38	2.0	42.8	1266	4326	1.7	4.8	9.5	3721	2.45	70.5	9.1	46.2	9.4	23	23.5	1.5	0.9	9	1.75
830947	Rock	1.32	11.5	40.4	12.4	7	0.3	0.9	0.2	39	1.53	10.4	1.4	21.0	5.2	20	<0.1	2.0	1.1	9	0.01
830948	Rock	0.99	2.4	44.8	12.7	40	0.2	3.5	6.8	127	4.18	11.6	2.4	20.6	6.8	15	0.1	0.8	2.3	14	0.04
830949	Rock	1.40	1.3	54.4	13.1	242	<0.1	7.4	11.1	1108	3.25	6.0	2.8	5.2	3.2	30	1.2	0.2	0.5	88	1.02
830950	Rock	1.48	1.3	37.5	10.5	123	<0.1	11.0	12.1	1057	5.05	18.5	0.1	1.0	0.4	53	0.3	2.4	0.3	51	1.78
830951	Rock	1.22	4.3	11.0	5.9	70	<0.1	6.0	3.4	504	1.58	24.5	<0.1	1.6	0.3	9	0.3	1.0	<0.1	7	0.44
830952	Rock	1.44	0.9	18.5	6.8	80	<0.1	9.9	6.7	586	2.41	32.0	<0.1	<0.5	0.3	168	0.1	1.5	<0.1	14	3.15
830953	Rock	1.53	1.2	39.2	5.5	109	<0.1	9.3	13.9	1068	4.88	21.4	0.2	<0.5	0.6	110	0.1	1.8	<0.1	78	2.67
830954	Rock	1.41	1.0	25.1	10.9	81	<0.1	4.2	7.0	757	4.24	9.8	0.4	<0.5	1.8	38	0.1	0.8	0.1	36	2.44
830955	Rock	1.40	6.6	28.4	6.2	124	0.3	5.3	9.8	845	3.03	37.5	0.3	5.9	0.9	104	0.5	1.9	<0.1	18	2.55



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**

110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo

Report Date: August 01, 2008

Page: 2 of 3 Part 2

CERTIFICATE OF ANALYSIS

SMI08000643.1

Method	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se	
Unit	%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
MDL	0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5	
726638	Rock	0.094	5	24	0.91	114	0.005	2	2.84	0.033	0.28	<0.1	<0.01	6.6	0.4	0.86	9	<0.5
726639	Rock	0.353	9	11	0.65	52	0.004	2	1.43	0.021	0.21	<0.1	0.07	10.2	0.4	2.34	5	1.2
726640	Rock	0.027	3	14	0.01	298	<0.001	4	0.36	0.017	0.19	<0.1	0.07	1.0	0.3	0.39	<1	0.5
726641	Rock	0.139	25	6	1.18	142	0.012	1	1.63	0.064	0.15	<0.1	0.04	3.7	0.2	0.91	7	1.9
726642	Rock	0.008	5	5	0.30	208	0.002	3	0.56	0.065	0.18	<0.1	0.07	8.0	0.2	0.41	2	0.7
726643	Rock	0.166	9	2	0.83	115	<0.001	4	0.56	0.018	0.26	<0.1	0.04	7.3	0.3	0.95	<1	2.6
726644	Rock	0.076	5	10	0.97	56	0.024	2	2.09	0.157	0.20	<0.1	<0.01	6.2	0.4	2.51	6	1.6
726645	Rock	0.011	4	2	0.42	87	<0.001	<1	0.91	0.053	0.16	<0.1	0.01	1.2	0.2	0.59	2	<0.5
726646	Rock	0.124	9	5	0.77	95	0.005	1	1.34	0.042	0.26	0.1	0.01	2.2	0.3	1.06	4	0.9
726647	Rock	0.062	3	6	0.75	90	0.003	1	2.10	0.043	0.32	<0.1	<0.01	2.9	0.3	1.88	5	0.9
726648	Rock	0.029	3	7	0.86	69	0.008	<1	2.71	0.044	0.24	<0.1	0.02	2.9	0.4	1.58	5	0.6
726649	Rock	0.147	6	6	1.55	136	0.022	2	2.04	0.059	0.24	<0.1	0.03	4.3	0.4	0.63	8	4.9
830938	Rock	0.116	13	3	0.25	28	<0.001	2	0.68	0.019	0.26	0.1	0.02	1.9	0.4	2.45	2	1.3
830939	Rock	0.202	9	5	0.90	44	0.220	4	3.73	0.550	0.06	0.3	<0.01	3.8	<0.1	0.16	14	<0.5
830940	Rock	0.006	<1	7	<0.01	177	<0.001	6	0.16	<0.001	0.13	<0.1	0.56	0.8	<0.1	0.47	<1	<0.5
830941	Rock	0.127	17	6	0.36	669	0.004	4	0.83	0.044	0.16	0.2	<0.01	3.6	0.1	<0.05	3	<0.5
830942	Rock	0.119	17	5	0.53	32	0.003	5	1.00	0.017	0.24	<0.1	0.01	5.1	0.3	2.19	4	1.8
830943	Rock	0.131	16	6	0.33	731	0.029	3	0.94	0.078	0.19	0.3	<0.01	4.9	0.2	0.12	4	<0.5
830944	Rock	0.138	17	5	0.73	187	0.009	3	1.64	0.033	0.17	0.2	<0.01	3.8	0.2	0.58	7	0.6
830945	Rock	0.042	7	12	0.08	59	<0.001	2	0.55	0.010	0.31	<0.1	<0.01	1.2	0.4	1.69	1	1.0
830946	Rock	0.108	25	3	0.42	53	<0.001	1	0.39	0.005	0.20	<0.1	0.01	1.4	0.3	1.79	<1	0.9
830947	Rock	0.021	23	3	0.21	117	0.003	<1	0.83	0.016	0.44	0.1	<0.01	0.5	0.3	0.05	2	2.6
830948	Rock	0.079	17	3	0.09	33	<0.001	2	0.59	0.010	0.25	0.1	0.02	1.0	0.2	2.52	1	2.0
830949	Rock	0.134	17	9	1.25	95	0.015	2	1.43	0.046	0.08	<0.1	<0.01	6.9	<0.1	1.12	7	<0.5
830950	Rock	0.106	5	8	1.02	54	0.002	1	1.12	0.035	0.16	<0.1	0.03	8.0	<0.1	2.22	5	1.5
830951	Rock	0.032	4	8	0.04	88	<0.001	1	0.22	0.037	0.10	<0.1	<0.01	3.1	<0.1	0.22	<1	0.5
830952	Rock	0.072	5	4	0.37	93	0.001	<1	0.34	0.017	0.21	<0.1	0.01	4.5	<0.1	0.68	<1	0.7
830953	Rock	0.121	9	9	1.24	91	0.003	2	1.34	0.049	0.21	<0.1	0.02	10.3	<0.1	1.46	6	1.0
830954	Rock	0.068	5	5	0.84	67	0.002	2	1.23	0.039	0.25	<0.1	0.02	5.1	0.1	1.96	5	1.3
830955	Rock	0.088	6	5	0.67	113	<0.001	2	0.33	0.026	0.17	<0.1	0.02	4.9	<0.1	1.18	<1	1.5



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.

Vancouver BC V6C 1Z7 Canada

Project:

Zymo

Report Date:

August 01, 2008

Page:

3 of 3

Part 1

CERTIFICATE OF ANALYSIS

SMI08000643.1

Method	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
Unit	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	
MDL	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	
830956	Rock	1.39	0.7	7.3	12.2	110	<0.1	4.4	8.1	843	2.46	11.0	<0.1	<0.5	0.3	88	0.5	1.9	<0.1	19	2.23
830957	Rock	1.38	0.7	2.0	5.2	20	<0.1	5.5	7.7	481	2.64	46.0	<0.1	<0.5	0.2	41	<0.1	0.8	0.2	11	1.40
830958	Rock	1.69	1.2	5.5	27.3	17	0.4	4.6	8.5	563	3.61	92.3	<0.1	4.6	0.3	54	<0.1	1.2	0.3	<2	1.97
830959	Rock	1.66	0.7	3.4	11.0	123	0.1	7.0	12.6	1699	5.54	17.4	<0.1	1.2	0.4	42	0.2	1.4	0.3	39	1.41
830960	Rock	1.35	2.1	1.9	2.8	54	<0.1	3.4	8.2	1123	3.01	2.1	2.2	<0.5	4.5	93	<0.1	0.2	0.3	39	3.52
830961	Rock	1.69	1.1	211.3	13.1	30	0.5	34.6	9.5	1003	5.86	23.2	0.1	22.6	0.4	35	0.2	0.3	5.2	12	0.76



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
Report Date: August 01, 2008

Page: 3 of 3 **Part** 2

CERTIFICATE OF ANALYSIS

SMI08000643.1

Method	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
Analyte	P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se	
Unit	%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
MDL	0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.01	0.05	1	0.5	
830956	Rock	0.104	4	7	0.39	37	0.002	<1	0.40	0.040	0.09	<0.1	0.01	3.7	<0.1	0.92	2	0.8
830957	Rock	0.035	3	5	0.44	76	<0.001	2	0.67	0.057	0.16	<0.1	0.02	3.4	<0.1	1.66	3	<0.5
830958	Rock	0.036	3	3	0.42	59	<0.001	1	0.37	0.045	0.19	<0.1	0.03	2.9	<0.1	2.80	<1	0.7
830959	Rock	0.087	4	10	1.73	53	0.005	1	2.16	0.036	0.10	<0.1	0.02	10.4	<0.1	1.97	10	<0.5
830960	Rock	0.162	32	3	0.99	118	0.004	1	2.24	0.047	0.15	<0.1	0.03	2.8	<0.1	0.28	6	<0.5
830961	Rock	0.017	1	15	0.42	19	<0.001	<1	0.16	0.004	0.05	<0.1	0.02	1.3	<0.1	5.33	<1	4.2

QUALITY CONTROL REPORT

SMI08000643.1

Method	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
Unit	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	
MDL	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	
Reference Materials																					
STD DS7	Standard	19.7	115.5	68.9	403	0.9	55.7	9.0	620	2.33	48.9	4.8	67.6	4.2	67	6.2	5.8	4.5	87	0.93	
STD DS7	Standard	22.5	112.1	69.9	398	0.9	56.6	9.7	634	2.39	49.7	4.9	64.4	4.4	75	6.2	6.0	4.4	89	0.96	
STD DS7	Standard	20.6	119.1	69.7	402	0.8	59.1	10.1	626	2.35	50.2	5.0	59.3	4.3	72	6.3	5.9	4.3	90	0.90	
STD DS7 Expected		20.9	109	70.6	411	0.9	56	9.7	627	2.39	48.2	4.9	70	4.4	69	6.4	5.9	4.5	86	0.93	
BLK	Blank	<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01	
BLK	Blank	<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01	
Prep Wash																					
G1	Prep Blank	<0.01	1.3	2.3	3.3	45	<0.1	4.7	4.4	542	1.79	<0.5	2.7	<0.5	4.8	65	<0.1	<0.1	<0.1	40	0.52
G1	Prep Blank	<0.01	1.2	2.8	3.7	47	<0.1	6.0	4.5	575	1.93	<0.5	2.7	<0.5	5.0	81	<0.1	<0.1	<0.1	43	0.69

QUALITY CONTROL REPORT

SMI08000643.1

Method		1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
Analyte	P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	TI	S	Ga	Se	
Unit	%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
MDL	0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5	
Reference Materials																		
STD DS7	Standard	0.076	13	204	1.02	369	0.118	40	1.00	0.086	0.42	3.8	0.20	2.3	3.9	0.19	5	3.6
STD DS7	Standard	0.076	13	209	1.04	390	0.131	41	1.04	0.089	0.42	3.8	0.22	2.4	4.3	0.19	5	3.6
STD DS7	Standard	0.076	13	202	1.04	393	0.126	40	1.00	0.093	0.43	3.7	0.20	2.6	4.1	0.18	5	3.4
STD DS7 Expected		0.08	13	163	1.05	370	0.124	39	0.959	0.073	0.44	3.8	0.2	2.5	4.2	0.21	4.6	3.5
BLK	Blank	<0.001	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
BLK	Blank	<0.001	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
Prep Wash																		
G1	Prep Blank	0.071	10	16	0.57	228	0.133	<1	1.16	0.089	0.48	0.2	<0.01	2.0	0.4	<0.05	5	<0.5
G1	Prep Blank	0.072	11	16	0.63	248	0.152	1	1.36	0.125	0.54	<0.1	<0.01	2.4	0.4	<0.05	6	<0.5



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.

Vancouver BC V6C 1Z7 Canada

Submitted By:

Glen Garratt

Receiving Lab:

Canada-Smithers

Received:

July 24, 2008

Report Date:

August 19, 2008

Page:

1 of 3

CERTIFICATE OF ANALYSIS

SMI08000656.1

CLIENT JOB INFORMATION

Project: Zymo
Shipment ID: zy-so-08-01
P.O. Number
Number of Samples: 43

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
DISP-RJT-SOIL Immediate Disposal of Soil Reject

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Mincord Exploration Consultants Ltd.
110 - 325 Howe St.
Vancouver BC V6C 1Z7
Canada

CC: Bob Johnston

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status
SS80	43	Dry at 60C sieve 100g to -80 mesh		
Dry at 60C	43	Dry at 60C		
1DX15	40	1:1:1 Aqua Regia digestion ICP-MS analysis	15	Completed

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only. All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**

110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo

Report Date: August 19, 2008

Page: 2 of 3 Part 1

CERTIFICATE OF ANALYSIS

SMI08000656.1

Method	Analyte	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
		Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	P
Unit		ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	%
MDL		0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	0.001
ZSP-08-001	Soil	1.2	29.2	10.4	58	0.3	28.7	6.8	196	4.16	12.5	0.8	3.7	0.7	17	0.2	0.5	0.2	63	0.09	0.082
ZSP-08-002	Soil	1.3	26.1	9.0	65	0.5	27.5	6.6	191	3.70	13.5	0.6	1.6	0.8	7	0.2	0.5	0.1	54	0.03	0.071
ZSP-08-003	Soil	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.
ZSP-08-004	Soil	1.1	23.0	9.4	51	<0.1	15.4	4.8	277	2.57	15.4	0.5	1.2	0.1	39	0.2	0.5	0.2	57	0.21	0.051
ZSP-08-005	Soil	0.9	17.4	9.4	57	<0.1	15.9	4.5	204	2.57	14.9	0.4	<0.5	0.3	42	0.2	0.5	0.2	58	0.24	0.035
ZSP-08-006	Soil	1.7	25.3	11.8	95	<0.1	27.5	14.5	1858	3.45	16.4	0.7	<0.5	0.4	57	0.3	0.6	0.2	60	0.29	0.074
ZSP-08-007	Soil	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.
ZSP-08-008	Soil	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.
ZSP-08-009	Soil	1.5	36.3	11.8	75	0.3	17.2	11.4	3121	3.79	22.2	1.8	1.1	0.2	111	0.6	0.5	0.2	58	0.66	0.088
ZSP-08-010	Soil	2.2	22.6	20.0	97	0.7	22.8	31.7	2630	5.43	26.2	0.6	0.8	1.0	60	0.4	0.7	0.2	74	0.49	0.067
ZSP-08-011	Soil	1.1	34.2	15.0	80	0.3	19.0	7.1	532	3.54	23.9	1.0	1.6	0.1	78	0.6	0.9	0.2	55	0.62	0.088
ZSP-08-012	Soil	0.9	19.3	10.2	70	0.1	14.4	5.5	344	3.11	24.4	0.4	0.5	0.3	30	0.2	1.2	0.2	67	0.22	0.040
ZSP-08-013	Soil	1.3	25.8	14.1	75	0.3	18.1	6.3	345	4.43	41.6	0.6	2.1	1.0	9	0.2	1.1	0.2	63	0.03	0.111
ZSP-08-014	Soil	1.0	22.0	9.6	70	0.3	19.0	7.3	432	3.70	18.7	0.5	2.0	0.8	7	0.2	0.7	0.1	67	0.02	0.070
ZSP-08-015	Soil	1.0	22.3	15.7	61	0.2	12.6	5.1	240	5.52	34.5	0.6	2.1	0.4	14	0.4	1.0	0.2	79	0.04	0.084
ZSP-08-016	Soil	1.2	31.5	19.2	111	0.5	22.2	10.7	874	3.64	39.8	0.9	1.9	0.1	39	0.4	1.3	0.2	62	0.24	0.105
ZSP-08-017	Soil	1.0	24.1	12.6	64	0.3	18.5	5.8	242	3.81	28.6	0.4	0.7	0.1	19	0.2	1.0	0.2	75	0.14	0.054
ZSP-08-018	Soil	1.2	21.6	13.6	92	<0.1	25.4	10.8	743	3.77	25.3	0.5	1.8	0.4	38	0.1	1.0	0.2	69	0.30	0.062
ZSP-08-019	Soil	2.6	10.8	11.7	104	0.2	21.1	19.6	3456	6.09	43.5	0.9	1.2	0.5	36	0.2	0.5	0.1	60	0.28	0.129
ZSP-08-020	Soil	0.8	22.5	11.2	52	0.2	11.1	5.3	419	2.81	20.4	0.6	<0.5	0.1	38	0.2	0.7	0.2	64	0.29	0.055
ZSP-08-021	Soil	0.7	12.7	12.5	91	0.6	32.7	7.7	446	2.65	22.0	1.8	<0.5	0.7	72	0.5	0.3	0.1	42	0.60	0.160
ZSP-08-022	Soil	1.2	42.3	13.1	101	0.4	31.9	10.3	445	4.30	24.7	0.7	2.6	1.3	8	0.2	1.1	0.2	64	0.03	0.054
ZSP-08-023	Soil	1.4	16.3	10.7	50	0.1	10.2	4.2	225	5.00	15.7	0.6	3.0	0.7	7	0.2	0.7	0.2	64	0.03	0.037
ZSP-08-024	Soil	1.2	17.2	12.8	47	0.2	12.2	4.4	263	5.16	17.8	0.5	2.0	0.5	10	0.3	0.7	0.2	82	0.06	0.056
ZSP-08-025	Soil	1.1	17.7	13.9	42	0.1	14.5	4.8	227	5.70	20.0	0.4	2.1	1.2	6	0.1	0.7	0.2	66	0.02	0.050
ZSP-08-026	Soil	1.5	15.9	12.8	47	0.3	9.6	3.6	206	5.11	18.2	0.7	5.0	0.5	12	0.3	0.8	0.2	75	0.06	0.069
ZSP-08-027	Soil	0.4	5.7	5.3	40	<0.1	17.4	4.6	134	1.41	4.7	0.4	2.0	1.6	17	<0.1	0.2	<0.1	33	0.16	0.076
ZSP-08-028	Soil	0.5	9.8	7.5	13	0.1	3.8	1.5	93	1.19	4.6	0.3	0.7	0.2	14	0.2	0.2	0.1	29	0.11	0.050
ZSP-08-029	Soil	0.8	5.8	7.4	16	<0.1	3.3	1.5	125	0.77	8.1	0.2	1.3	<0.1	6	<0.1	0.5	0.2	44	0.02	0.019
ZSP-08-030	Soil	1.1	11.2	10.5	53	<0.1	14.4	26.3	2815	2.41	8.0	0.5	1.8	0.7	14	0.4	0.4	0.1	46	0.11	0.120

This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
 Report Date: August 19, 2008

Page: 2 of 3 Part 2

CERTIFICATE OF ANALYSIS

SMI08000656.1

Method	Analyte	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
		La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
Unit		ppm	ppm	%	ppm	%	ppm	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
MDL		1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.01	0.01	0.01	0.05	1	0.5	
ZSP-08-001	Soil	5	30	0.33	97	0.004	2	2.40	0.006	0.05	<0.1	0.12	2.6	0.1	<0.05	8	0.5
ZSP-08-002	Soil	5	26	0.35	63	0.005	2	2.45	0.005	0.04	<0.1	0.14	2.3	0.1	<0.05	7	<0.5
ZSP-08-003	Soil	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.
ZSP-08-004	Soil	6	18	0.23	277	0.008	1	1.41	0.007	0.07	0.1	0.03	1.2	0.1	<0.05	7	<0.5
ZSP-08-005	Soil	6	19	0.27	390	0.007	<1	1.55	0.007	0.05	<0.1	0.02	1.9	<0.1	<0.05	8	<0.5
ZSP-08-006	Soil	7	25	0.37	362	0.007	1	2.05	0.008	0.09	<0.1	0.04	2.7	0.2	<0.05	8	<0.5
ZSP-08-007	Soil	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.
ZSP-08-008	Soil	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.
ZSP-08-009	Soil	10	14	0.26	635	0.011	2	2.05	0.008	0.06	<0.1	0.08	1.9	0.2	<0.05	7	0.7
ZSP-08-010	Soil	4	24	0.37	270	0.006	2	2.99	0.007	0.08	0.1	0.06	3.6	0.2	<0.05	9	<0.5
ZSP-08-011	Soil	10	12	0.34	797	0.019	1	1.86	0.009	0.06	0.1	0.07	2.0	0.1	<0.05	7	0.5
ZSP-08-012	Soil	5	16	0.27	440	0.012	<1	1.77	0.007	0.04	<0.1	0.03	2.2	<0.1	<0.05	8	<0.5
ZSP-08-013	Soil	5	20	0.26	72	0.012	2	2.85	0.006	0.04	<0.1	0.16	3.0	<0.1	<0.05	7	<0.5
ZSP-08-014	Soil	5	22	0.25	103	0.009	1	2.26	0.005	0.05	<0.1	0.07	3.0	0.1	<0.05	8	<0.5
ZSP-08-015	Soil	4	12	0.25	111	0.013	1	2.19	0.006	0.05	0.1	0.12	2.5	<0.1	<0.05	9	<0.5
ZSP-08-016	Soil	9	13	0.35	445	0.013	3	2.27	0.009	0.07	0.1	0.05	1.7	0.1	<0.05	9	<0.5
ZSP-08-017	Soil	5	19	0.25	226	0.009	1	1.67	0.005	0.07	<0.1	0.05	1.7	0.1	<0.05	9	<0.5
ZSP-08-018	Soil	6	24	0.43	704	0.012	2	1.84	0.009	0.07	<0.1	0.03	2.8	<0.1	<0.05	7	<0.5
ZSP-08-019	Soil	10	14	0.33	649	0.009	2	2.08	0.013	0.05	<0.1	0.09	3.6	0.3	<0.05	6	<0.5
ZSP-08-020	Soil	5	14	0.21	635	0.006	<1	1.48	0.006	0.06	<0.1	0.02	1.2	0.1	<0.05	7	<0.5
ZSP-08-021	Soil	16	13	0.29	735	0.006	3	2.26	0.013	0.07	<0.1	0.15	4.4	0.3	0.08	4	0.6
ZSP-08-022	Soil	5	31	0.40	81	0.008	2	2.87	0.006	0.06	<0.1	0.11	4.1	0.1	<0.05	8	<0.5
ZSP-08-023	Soil	6	14	0.24	50	0.025	1	3.06	0.008	0.04	0.1	0.12	3.3	<0.1	<0.05	9	0.9
ZSP-08-024	Soil	6	19	0.21	89	0.013	2	2.55	0.006	0.05	0.1	0.07	2.7	0.1	<0.05	12	<0.5
ZSP-08-025	Soil	4	19	0.25	48	0.009	<1	2.26	0.005	0.03	0.1	0.12	2.7	<0.1	<0.05	7	<0.5
ZSP-08-026	Soil	5	9	0.21	74	0.029	2	2.87	0.005	0.03	0.2	0.13	2.6	<0.1	<0.05	10	0.7
ZSP-08-027	Soil	6	20	0.21	192	0.001	2	1.62	0.005	0.06	<0.1	0.03	1.2	<0.1	<0.05	6	<0.5
ZSP-08-028	Soil	6	6	0.04	124	0.004	1	1.39	0.004	0.03	<0.1	0.03	0.6	<0.1	<0.05	5	<0.5
ZSP-08-029	Soil	4	6	0.02	29	0.013	2	0.62	0.004	0.03	0.1	0.01	0.5	<0.1	<0.05	8	<0.5
ZSP-08-030	Soil	5	13	0.21	217	0.003	1	2.49	0.005	0.05	0.1	0.05	1.4	0.1	<0.05	7	<0.5

This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
 Report Date: August 19, 2008

Page: 3 of 3 Part 1

CERTIFICATE OF ANALYSIS

SMI08000656.1

Method	Analyte	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
		Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	P
Unit		ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	%
MDL		0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	0.001
ZSP-08-031	Soil	1.2	21.3	9.8	61	0.2	11.7	4.8	556	2.97	24.6	0.7	1.8	0.1	46	0.3	0.9	0.2	54	0.30	0.059
ZSP-08-032	Soil	1.7	22.4	13.7	59	0.2	16.1	6.6	398	5.00	30.2	1.0	2.7	0.2	16	0.3	1.0	0.2	74	0.09	0.072
ZSP-08-033	Soil	1.2	13.9	13.6	46	0.1	7.9	4.6	428	3.98	30.3	0.5	3.6	0.2	14	0.1	1.0	0.3	84	0.07	0.052
ZSP-08-034	Soil	0.9	20.2	10.3	47	0.3	11.9	6.2	476	2.73	14.2	0.6	1.4	0.1	18	0.3	0.6	0.2	60	0.09	0.053
ZSP-08-035	Soil	1.3	40.8	12.6	39	0.2	11.1	5.0	357	3.81	20.5	1.4	2.4	0.2	14	0.3	0.9	0.2	65	0.08	0.055
ZSP-08-036	Soil	1.1	20.7	11.0	67	<0.1	19.9	8.6	514	4.22	23.1	0.7	1.7	0.5	20	<0.1	1.0	0.1	54	0.09	0.048
ZSP-08-037	Soil	0.8	17.0	11.8	30	0.2	11.3	2.8	114	1.72	12.1	0.4	1.2	<0.1	12	0.2	0.6	0.2	58	0.08	0.036
ZSP-08-038	Soil	0.8	17.3	12.6	54	0.1	18.8	7.9	512	3.44	19.6	0.4	<0.5	0.2	15	0.1	0.7	0.2	68	0.10	0.058
ZSP-08-039	Soil	1.6	36.5	15.1	83	0.2	24.8	12.5	922	4.79	23.9	1.0	3.1	0.4	15	0.3	1.1	0.2	64	0.08	0.054
ZSP-08-040	Soil	1.1	19.1	8.5	30	0.2	6.8	3.2	129	1.67	8.2	0.9	2.1	<0.1	13	0.3	0.4	0.1	37	0.05	0.071
ZSP-08-041	Soil	1.1	39.0	14.5	57	0.6	15.2	5.3	283	3.32	19.8	1.2	2.7	0.1	24	0.3	0.8	0.2	54	0.08	0.075
ZSP-08-042	Soil	1.0	22.3	9.2	61	0.2	18.5	7.4	451	3.03	16.9	0.7	1.5	0.2	14	0.3	0.8	0.2	57	0.06	0.047
ZSP-08-043	Soil	1.2	33.7	15.0	60	0.6	13.9	5.0	297	3.65	19.8	0.8	4.2	0.1	9	0.2	0.7	0.2	73	0.05	0.065



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**

110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo

Report Date: August 19, 2008

Page: 3 of 3 Part 2

CERTIFICATE OF ANALYSIS

SMI08000656.1

Method	Analyte	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
		La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
Unit		ppm	ppm	%	ppm	%	ppm	%	%	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm
MDL		1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.05	1	0.5	
ZSP-08-031	Soil	7	10	0.31	227	0.013	1	2.24	0.006	0.06	<0.1	0.05	1.4	0.1	<0.05	9	<0.5
ZSP-08-032	Soil	7	17	0.36	84	0.019	2	3.29	0.007	0.05	0.2	0.13	2.7	0.2	<0.05	12	0.6
ZSP-08-033	Soil	6	9	0.21	94	0.019	1	2.10	0.005	0.05	0.2	0.07	2.2	0.1	<0.05	12	<0.5
ZSP-08-034	Soil	6	13	0.24	96	0.010	<1	2.11	0.007	0.05	0.1	0.05	1.5	0.1	<0.05	10	<0.5
ZSP-08-035	Soil	9	10	0.16	69	0.014	2	2.28	0.005	0.05	0.2	0.10	1.9	0.1	<0.05	8	0.6
ZSP-08-036	Soil	7	17	0.47	80	0.022	3	2.63	0.007	0.06	0.1	0.09	3.4	<0.1	<0.05	7	0.7
ZSP-08-037	Soil	5	16	0.12	87	0.008	1	1.41	0.004	0.06	0.1	0.05	0.9	0.1	<0.05	8	<0.5
ZSP-08-038	Soil	5	20	0.26	122	0.007	2	1.92	0.005	0.06	<0.1	0.05	1.4	0.1	<0.05	9	<0.5
ZSP-08-039	Soil	7	20	0.38	87	0.014	2	2.64	0.008	0.08	0.1	0.11	3.0	0.1	<0.05	8	0.5
ZSP-08-040	Soil	9	8	0.10	95	0.008	2	2.54	0.005	0.04	0.1	0.11	1.0	0.2	<0.05	7	0.6
ZSP-08-041	Soil	8	14	0.30	130	0.008	<1	2.80	0.007	0.07	0.1	0.13	1.6	0.2	<0.05	9	0.6
ZSP-08-042	Soil	7	19	0.33	76	0.013	1	2.36	0.005	0.05	0.1	0.09	2.1	0.1	<0.05	9	<0.5
ZSP-08-043	Soil	6	14	0.27	91	0.012	1	2.20	0.006	0.06	0.2	0.12	1.8	0.1	<0.05	12	<0.5

QUALITY CONTROL REPORT

SMI08000656.1

Method	Analyte	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
		Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	P
Unit		ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	%
MDL		0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	0.001
Pulp Duplicates																					
ZSP-08-009	Soil	1.5	36.3	11.8	75	0.3	17.2	11.4	3121	3.79	22.2	1.8	1.1	0.2	111	0.6	0.5	0.2	58	0.66	0.088
REP ZSP-08-009	QC	1.6	34.3	11.5	71	0.3	17.1	10.8	2982	3.53	22.0	1.8	<0.5	0.2	110	0.5	0.5	0.2	53	0.60	0.089
ZSP-08-032	Soil	1.7	22.4	13.7	59	0.2	16.1	6.6	398	5.00	30.2	1.0	2.7	0.2	16	0.3	1.0	0.2	74	0.09	0.072
REP ZSP-08-032	QC	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.
Reference Materials																					
STD DS7	Standard	19.1	105.2	71.2	402	0.9	53.4	8.6	618	2.30	50.9	4.7	56.8	4.0	72	6.0	5.8	4.7	77	0.95	0.074
STD DS7	Standard	21.2	119.2	67.9	434	0.9	58.3	9.9	673	2.47	55.4	4.7	70.8	4.1	71	6.3	6.1	4.2	90	0.93	0.080
STD DS7 Expected		20.9	109	70.6	411	0.9	56	9.7	627	2.39	48.2	4.9	70	4.4	69	6.4	5.9	4.5	86	0.93	0.08
BLK	Blank	<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01	<0.001
BLK	Blank	<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01	<0.001

QUALITY CONTROL REPORT

SMI08000656.1

Method	Analyte	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
		La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
Unit		ppm	ppm	%	ppm	%	ppm	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
MDL		1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.05	1	0.5	
Pulp Duplicates																	
ZSP-08-009	Soil	10	14	0.26	635	0.011	2	2.05	0.008	0.06	<0.1	0.08	1.9	0.2	<0.05	7	0.7
REP ZSP-08-009	QC	9	11	0.27	584	0.014	2	1.98	0.008	0.06	0.1	0.08	1.9	0.2	<0.05	7	<0.5
ZSP-08-032	Soil	7	17	0.36	84	0.019	2	3.29	0.007	0.05	0.2	0.13	2.7	0.2	<0.05	12	0.6
REP ZSP-08-032	QC	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.
Reference Materials																	
STD DS7	Standard	13	181	0.97	402	0.111	39	0.97	0.093	0.46	4.1	0.21	2.4	4.3	0.17	5	3.7
STD DS7	Standard	12	206	1.08	405	0.121	41	1.05	0.097	0.47	4.3	0.22	2.5	4.6	0.21	5	3.5
STD DS7 Expected		13	163	1.05	370	0.124	39	0.959	0.073	0.44	3.8	0.2	2.5	4.2	0.21	5	3.5
BLK	Blank	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
BLK	Blank	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.

Vancouver BC V6C 1Z7 Canada

Submitted By:

Glen Garratt

Receiving Lab:

Canada-Smithers

Received:

July 24, 2008

Report Date:

August 08, 2008

Page:

1 of 2

CERTIFICATE OF ANALYSIS

SMI08000657.1

CLIENT JOB INFORMATION

Project: Zymo
Shipment ID: zy-st-08-04
P.O. Number
Number of Samples: 4

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
DISP-RJT-SOIL Immediate Disposal of Soil Reject

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Mincord Exploration Consultants Ltd.
110 - 325 Howe St.
Vancouver BC V6C 1Z7
Canada

CC: Bob Johnston

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status
SS80	4	Dry at 60C sieve 100g to -80 mesh		
Dry at 60C	4	Dry at 60C		
1DX15	4	1:1:1 Aqua Regia digestion ICP-MS analysis	15	Completed

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only. All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.



AcmeLabs ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
Report Date: August 08, 2008

Page: 2 of 2 **Part** 1

CERTIFICATE OF ANALYSIS

SMI08000657.1

Method	Analyte	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
		Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	P
		ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	%
		MDL	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01
ZXB-08-014	Silt	1.6	19.7	15.8	88	0.1	18.4	34.8	8846	5.52	21.5	0.4	3.4	0.6	31	0.6	0.5	0.2	44	0.23	0.083
ZXB-08-015	Silt	4.0	58.7	34.0	173	0.2	30.1	34.7	>10000	5.23	26.6	0.6	6.3	0.9	71	1.4	0.9	0.3	48	0.46	0.101
ZXB-08-016	Silt	4.5	82.8	28.0	108	0.3	17.5	41.2	4489	7.58	33.8	0.8	9.0	1.0	57	0.6	0.9	0.2	52	0.29	0.115
ZXR-08-034	Silt	2.0	93.6	77.9	413	0.8	22.0	20.2	1578	5.61	77.8	0.8	30.3	1.7	33	2.0	3.1	1.8	47	0.45	0.076



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.

Vancouver BC V6C 1Z7 Canada

Project:

Zymo

Report Date:

August 08, 2008

Page:

2 of 2

Part 2

CERTIFICATE OF ANALYSIS

SMI08000657.1

Method	Analyte	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
		La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
Unit		ppm	ppm	%	ppm	%	ppm	%	%	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm
MDL		1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.05	1	0.5	
ZXB-08-014	Silt	5	12	0.26	231	0.003	1	1.42	0.006	0.04	<0.1	0.08	2.5	0.2	<0.05	5	<0.5
ZXB-08-015	Silt	7	17	0.30	410	0.003	2	1.63	0.009	0.06	<0.1	0.09	3.7	0.3	0.05	5	1.4
ZXB-08-016	Silt	11	11	0.30	155	0.002	1	1.73	0.006	0.05	<0.1	0.09	3.4	0.3	0.08	5	1.0
ZXR-08-034	Silt	6	13	0.40	82	0.016	3	0.80	0.027	0.06	0.1	0.07	4.3	0.1	2.23	3	2.2

QUALITY CONTROL REPORT

SMI08000657.1

Method	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
Analyte	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	P	
Unit	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	%	
MDL	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	0.001	
Reference Materials																					
STD DS7	Standard	19.2	105.5	64.9	375	0.8	54.8	8.9	606	2.24	47.3	4.5	56.8	3.9	67	5.9	5.3	4.1	83	0.88	0.068
STD DS7 Expected		20.9	109	70.6	411	0.9	56	9.7	627	2.39	48.2	4.9	70	4.4	69	6.4	5.9	4.5	86	0.93	0.08
BLK	Blank	<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	9	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01	<0.001

QUALITY CONTROL REPORT

SMI08000657.1

Method	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se	
Unit	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
MDL	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5	
Reference Materials																	
STD DS7	Standard	12	199	0.99	374	0.118	39	0.95	0.089	0.43	3.7	0.20	2.3	4.1	0.15	5	3.6
STD DS7 Expected		13	163	1.05	370	0.124	39	0.959	0.073	0.44	3.8	0.2	2.5	4.2	0.21	5	3.5
BLK	Blank	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.

Vancouver BC V6C 1Z7 Canada

Submitted By:

Glen Garratt

Receiving Lab:

Canada-Smithers

Received:

July 24, 2008

Report Date:

August 08, 2008

Page:

1 of 2

CERTIFICATE OF ANALYSIS

SMI08000658.1

CLIENT JOB INFORMATION

Project: Zymo
Shipment ID: zy-rk-08-08
P.O. Number
Number of Samples: 18

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
DISP-RJT Dispose of Reject After 90 days

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Mincord Exploration Consultants Ltd.
110 - 325 Howe St.
Vancouver BC V6C 1Z7
Canada

CC: Bob Johnston

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status
R150	18	Crush, split and pulverize rock to 200 mesh		
1DX15	18	1:1:1 Aqua Regia digestion ICP-MS analysis	15	Completed

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only. All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
 Report Date: August 08, 2008

Page: 2 of 2 Part 1

CERTIFICATE OF ANALYSIS

SMI08000658.1

Method	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
Unit	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	ppm	
MDL	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	
726650	Rock	3.03	22.4	734.3	11.3	41	0.3	5.4	18.0	240	3.34	3.0	1.0	28.9	5.8	60	0.2	0.1	<0.1	89	0.97
726651	Rock	2.36	23.8	692.9	8.8	45	0.2	5.1	17.6	388	3.12	6.1	1.3	17.1	5.9	91	0.2	0.3	0.1	65	1.36
726652	Rock	3.86	25.2	556.1	3.4	41	0.2	5.4	9.3	288	4.11	2.1	1.1	50.8	5.0	124	<0.1	<0.1	<0.1	118	1.25
726653	Rock	2.13	42.4	579.2	48.7	34	0.2	7.0	14.2	331	1.36	5.2	0.4	19.9	1.8	38	1.1	0.1	<0.1	17	1.04
726654	Rock	2.39	48.6	842.3	34.0	65	0.4	7.1	11.8	405	2.69	3.6	0.8	60.4	3.2	85	0.2	<0.1	<0.1	102	0.96
726655	Rock	3.06	59.5	1037	27.1	26	0.3	6.7	21.5	449	1.59	2.5	0.6	36.4	2.2	28	0.2	0.2	0.2	33	0.31
726656	Rock	2.74	207.4	1080	7.0	33	0.3	8.6	12.3	446	2.54	1.2	0.4	41.0	1.9	32	0.2	0.2	0.1	30	0.51
726657	Rock	2.33	94.1	1527	16.7	59	0.3	5.6	24.9	234	3.06	18.4	2.4	46.2	8.0	60	0.3	2.6	0.1	14	1.60
726658	Rock	3.33	106.3	1356	14.7	40	0.4	5.9	16.8	969	3.08	13.2	1.2	64.6	4.0	78	0.2	0.9	0.1	17	2.73
726659	Rock	2.81	95.8	1253	11.5	47	0.3	4.4	20.9	312	3.20	10.3	2.5	42.1	7.6	142	0.3	6.7	0.1	21	1.88
726660	Rock	2.21	235.2	567.0	8.0	29	0.2	8.0	10.9	483	2.05	1.2	0.6	25.4	2.0	36	0.2	0.1	0.1	36	1.18
726661	Rock	2.54	102.4	2651	9.0	78	0.5	8.2	49.7	454	4.58	37.3	1.5	48.9	4.9	51	0.4	48.0	0.1	53	0.61
726662	Rock	2.13	51.7	626.5	6.9	36	0.2	10.0	16.8	509	2.76	2.5	0.4	23.4	2.4	42	0.1	0.2	0.1	33	1.06
726663	Rock	2.57	38.7	1049	24.0	47	0.2	6.3	21.8	564	3.66	147.7	0.8	29.4	2.3	67	0.3	30.9	<0.1	13	3.17
726664	Rock	3.13	59.6	1288	11.3	50	0.4	5.0	20.4	788	4.39	25.4	1.5	43.5	3.7	81	0.3	2.2	0.1	20	4.00
726665	Rock	2.86	98.6	2220	10.2	39	0.7	5.5	26.5	336	3.94	34.4	2.2	95.2	5.3	53	0.2	2.3	0.2	17	1.80
726666	Rock	3.50	24.4	480.9	14.4	45	0.2	5.0	9.6	444	2.52	17.9	4.3	28.7	8.4	32	0.1	0.6	<0.1	26	2.23
726667	Rock	2.61	2.2	35.3	9.1	66	<0.1	3.2	12.5	624	3.71	0.7	0.7	8.2	2.2	50	0.1	0.2	0.2	66	1.74



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
 Report Date: August 08, 2008

Page: 2 of 2 Part 2

CERTIFICATE OF ANALYSIS

SMI08000658.1

Method	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se	
Unit	%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
MDL	0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5	
726650	Rock	0.158	10	6	1.41	163	0.149	<1	1.93	0.111	0.12	0.2	0.06	6.2	0.1	0.75	7	0.6
726651	Rock	0.148	16	4	1.10	161	0.045	2	1.49	0.062	0.19	<0.1	0.12	4.8	0.2	0.62	6	<0.5
726652	Rock	0.182	12	7	1.82	114	0.264	<1	2.88	0.240	0.37	<0.1	0.05	8.7	0.4	0.14	9	<0.5
726653	Rock	0.027	12	3	0.31	270	0.001	2	1.16	0.031	0.62	<0.1	0.04	3.1	0.4	0.44	3	<0.5
726654	Rock	0.122	11	9	1.05	262	0.125	2	2.04	0.174	0.33	0.2	0.18	8.2	0.2	0.29	7	<0.5
726655	Rock	0.052	17	4	0.34	347	0.002	2	1.20	0.040	0.45	<0.1	0.09	3.5	0.3	0.23	3	<0.5
726656	Rock	0.025	11	3	0.37	212	0.003	<1	1.35	0.028	0.49	<0.1	0.02	3.2	0.3	0.54	3	<0.5
726657	Rock	0.144	12	3	0.30	39	0.001	3	0.73	0.020	0.33	<0.1	0.21	2.8	0.2	2.23	2	2.5
726658	Rock	0.094	17	2	0.61	88	<0.001	4	0.57	0.019	0.34	<0.1	0.14	4.4	0.2	1.32	1	0.8
726659	Rock	0.149	19	2	0.49	45	<0.001	2	0.66	0.022	0.25	<0.1	0.10	3.5	0.2	1.65	2	1.1
726660	Rock	0.061	10	4	0.53	179	0.002	2	1.27	0.032	0.39	<0.1	0.03	3.4	0.2	0.36	4	<0.5
726661	Rock	0.193	38	2	0.48	270	0.010	2	1.33	0.027	0.42	<0.1	0.24	7.1	0.4	0.34	3	0.9
726662	Rock	0.056	7	3	0.61	219	0.006	2	1.47	0.028	0.49	<0.1	0.02	3.4	0.3	0.64	4	<0.5
726663	Rock	0.145	6	2	0.68	100	<0.001	4	0.54	0.008	0.27	<0.1	0.14	6.3	0.2	1.40	1	1.5
726664	Rock	0.134	8	2	0.89	71	<0.001	3	0.53	0.008	0.26	<0.1	0.40	4.5	0.2	1.96	1	1.5
726665	Rock	0.139	9	2	0.35	64	<0.001	5	0.59	0.010	0.32	<0.1	0.15	3.6	0.3	1.98	1	1.6
726666	Rock	0.159	18	2	0.13	266	<0.001	4	0.67	0.009	0.26	<0.1	0.47	5.4	0.4	0.16	<1	<0.5
726667	Rock	0.190	14	3	0.87	52	0.119	1	1.88	0.061	0.09	0.2	0.02	2.2	<0.1	1.04	8	<0.5

QUALITY CONTROL REPORT

SMI08000658.1

Method	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
Unit	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	
MDL	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	
Reference Materials																					
STD DS7	Standard	18.8	99.8	82.3	382	0.8	52.9	9.0	613	2.35	52.0	5.9	69.7	5.1	74	6.2	6.7	5.1	82	0.89	
STD DS7	Standard	20.1	107.5	71.4	386	0.8	54.9	9.4	627	2.42	49.4	5.0	56.5	4.6	73	5.9	5.9	4.4	84	0.94	
STD DS7 Expected		20.9	109	70.6	411	0.9	56	9.7	627	2.39	48.2	4.9	70	4.4	69	6.4	5.9	4.5	86	0.93	
BLK	Blank	<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	3.3	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01	
Prep Wash																					
G1	Prep Blank	<0.01	1.5	2.5	3.7	43	<0.1	5.9	4.3	530	1.78	0.8	2.7	1.4	4.6	75	<0.1	<0.1	<0.1	33	0.52
G1	Prep Blank	<0.01	0.5	2.4	3.5	45	<0.1	4.3	4.2	557	1.79	3.8	2.8	1.0	4.7	59	<0.1	<0.1	<0.1	33	0.45

QUALITY CONTROL REPORT

SMI08000658.1

Method		1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte		P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
Unit		%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm
MDL		0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5
Reference Materials																		
STD DS7	Standard	0.081	13	194	1.04	397	0.117	43	1.00	0.090	0.47	3.9	0.22	2.4	4.1	0.18	4	1.3
STD DS7	Standard	0.076	13	200	1.04	369	0.130	40	1.02	0.092	0.47	3.7	0.19	2.4	3.4	0.19	5	1.5
STD DS7 Expected		0.08	13	163	1.05	370	0.124	39	0.959	0.073	0.44	3.8	0.2	2.5	4.2	0.21	4.6	3.5
BLK	Blank	<0.001	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
Prep Wash																		
G1	Prep Blank	0.074	8	10	0.55	231	0.128	<1	1.07	0.105	0.55	<0.1	<0.01	2.2	0.3	<0.05	5	<0.5
G1	Prep Blank	0.075	7	11	0.58	226	0.120	<1	0.95	0.056	0.53	<0.1	<0.01	1.7	0.2	<0.05	5	<0.5



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.

Vancouver BC V6C 1Z7 Canada

Submitted By:

Glen Garratt

Receiving Lab:

Canada-Smithers

Received:

July 28, 2008

Report Date:

August 19, 2008

Page:

1 of 3

CERTIFICATE OF ANALYSIS

SMI08000664.1

CLIENT JOB INFORMATION

Project: Zymo
Shipment ID: zy-so-08-02
P.O. Number
Number of Samples: 54

SAMPLE DISPOSAL

RTRN-PLP Return
DISP-RJT-SOIL Immediate Disposal of Soil Reject

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Mincord Exploration Consultants Ltd.
110 - 325 Howe St.
Vancouver BC V6C 1Z7
Canada

CC: Bob Johnston

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status
SS80	54	Dry at 60C sieve 100g to -80 mesh		
Dry at 60C	54	Dry at 60C		
1DX15	54	1:1:1 Aqua Regia digestion ICP-MS analysis	15	Completed

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only. All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

ACME ANALYTICAL LABORATORIES LTD.

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project:

Zymo

Report Date:

August 19, 2008

Page:

2 of 3

Part 1

CERTIFICATE OF ANALYSIS

SMI08000664.1

Method Analyte	Unit	MDL	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
			Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	P
			ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	%	
			0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	0.001
L108W 11200 N	Soil		4.1	110.1	125.3	207	0.6	13.3	10.3	781	6.68	33.6	1.6	25.2	1.5	11	0.5	2.5	2.1	76	0.10	0.164
L108W 11250 N	Soil		2.7	61.4	45.2	66	0.8	4.7	2.7	141	3.72	21.3	1.5	10.5	0.3	5	0.3	1.4	1.3	80	0.01	0.053
L108W 11300 N	Soil		3.1	122.8	82.7	151	1.8	10.1	9.0	819	4.61	26.8	3.7	24.7	1.1	11	0.2	1.8	1.6	64	0.05	0.155
L108W 11350 N	Soil		2.7	107.2	221.9	137	0.4	10.8	8.2	688	7.28	30.2	1.8	20.3	2.7	12	0.4	2.1	1.6	76	0.10	0.222
L108W 11400 N	Soil		4.4	168.2	97.8	157	1.8	7.4	7.0	619	6.07	47.4	2.1	33.2	0.6	12	0.3	2.8	1.9	77	0.07	0.119
L108W 11450 N	Soil		3.6	147.7	50.1	133	2.6	8.4	3.7	212	3.89	28.4	2.3	107.2	0.6	17	0.2	2.0	2.2	57	0.12	0.096
L108W 11500 N	Soil		3.4	173.4	89.9	160	2.9	8.4	7.6	368	1.77	18.5	2.6	28.4	0.5	25	0.9	1.2	1.3	45	0.24	0.178
L108W 11550 N	Soil		2.5	65.1	56.1	73	1.4	4.6	5.3	1102	2.56	19.1	1.2	42.6	0.4	14	0.2	1.1	2.8	49	0.10	0.050
L108W 11600 N	Soil		6.9	108.2	57.3	119	0.9	5.9	8.3	583	14.92	79.9	1.7	20.7	1.2	31	0.2	1.3	1.2	44	0.12	0.100
L108W 11650 N	Soil		2.7	134.5	164.7	226	0.5	17.7	10.9	409	5.85	31.3	1.2	25.0	3.3	11	0.4	1.6	1.2	65	0.05	0.062
L108W 11700 N	Soil		6.0	142.1	267.0	176	1.8	9.1	13.1	1172	10.47	89.6	3.4	78.3	1.1	13	0.6	3.0	6.3	75	0.11	0.218
L108W 11750 N	Soil		3.9	105.5	122.7	146	1.8	9.4	7.0	588	7.29	45.6	2.4	54.3	0.6	9	0.4	4.8	3.5	82	0.05	0.119
L108W 11800 N	Soil		3.9	131.4	52.7	132	0.6	10.6	5.3	395	4.62	31.4	1.2	23.9	0.3	24	0.2	2.3	1.3	68	0.26	0.091
L108W 11850 N	Soil		3.9	61.5	44.1	71	0.4	3.2	2.5	150	3.47	32.3	0.8	88.7	0.3	23	0.1	2.5	1.2	77	0.18	0.042
L108W 11900 N	Soil		3.4	37.0	8.4	41	0.4	1.5	1.1	56	1.35	17.1	0.4	24.6	0.9	5	<0.1	1.3	0.5	57	<0.01	0.015
L108W 11950 N	Soil		2.2	64.9	66.1	134	1.5	8.0	5.9	1082	3.58	20.7	2.0	12.6	0.2	15	0.3	1.2	1.3	58	0.08	0.112
L108W 12000 N	Soil		3.8	160.5	137.7	150	0.6	8.8	5.7	591	5.94	46.5	1.0	37.0	0.8	12	0.3	3.5	2.3	66	0.06	0.208
L108W 12050 N	Soil		2.0	72.3	114.9	128	0.5	12.7	11.4	1360	6.60	27.8	1.1	30.2	1.7	10	0.3	1.6	1.5	64	0.07	0.123
L108W 12100 N	Soil		2.0	76.8	83.3	113	0.8	8.3	5.3	167	3.57	21.8	1.8	29.8	0.7	11	0.2	1.1	2.0	87	0.09	0.122
L108W 12150 N	Soil		2.8	59.3	68.2	80	0.8	6.7	4.1	206	6.76	32.1	1.1	14.5	1.1	7	0.4	1.2	1.7	81	0.03	0.074
L108W 12200 N	Soil		2.0	45.2	73.5	104	3.7	8.1	8.2	795	6.20	25.2	1.0	7.7	0.5	10	0.5	1.3	1.1	74	0.07	0.197
L108W 12250 N	Soil		1.8	54.4	35.8	88	1.1	8.5	5.2	1325	4.56	22.8	1.3	8.5	0.2	26	0.2	1.0	1.1	81	0.16	0.098
L108W 12300 N	Soil		1.7	41.4	24.8	94	0.2	13.9	6.7	316	4.66	17.6	0.8	4.9	0.2	14	0.4	1.0	0.4	74	0.05	0.086
ZSP-08-044	Soil		3.0	78.8	66.6	835	1.4	20.6	16.9	3374	4.15	1220	1.7	13.7	0.7	85	5.8	1.6	0.6	48	0.50	0.091
ZSP-08-045	Soil		1.9	37.4	24.7	77	0.2	13.8	7.4	523	5.28	31.4	0.7	6.8	1.0	11	0.2	1.3	0.4	86	0.04	0.043
ZSP-08-046	Soil		1.4	25.6	22.8	62	0.4	7.7	4.0	292	4.15	35.9	0.4	8.4	0.5	10	<0.1	1.6	0.5	89	0.02	0.076
ZSP-08-047	Soil		1.5	61.7	44.6	98	0.4	11.1	5.9	435	7.82	58.0	0.7	9.7	0.8	8	0.3	2.3	1.2	94	0.02	0.085
ZSP-08-048	Soil		0.9	150.6	19.2	64	0.3	8.2	10.9	4114	2.99	22.6	0.8	3.3	0.1	12	0.5	1.4	0.4	74	0.03	0.053
ZSP-08-049	Soil		1.4	26.8	45.2	97	1.8	9.5	5.1	411	5.48	49.4	0.6	5.6	0.9	11	0.2	2.3	0.9	99	0.02	0.081
ZSP-08-050	Soil		1.5	52.3	67.9	121	1.4	6.2	4.1	633	5.64	57.7	0.6	56.2	0.5	11	0.2	2.5	2.6	73	0.02	0.100

This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
 Report Date: August 19, 2008

Page: 2 of 3 Part 2

CERTIFICATE OF ANALYSIS

SMI08000664.1

Method	Analyte	Unit	MDL	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
				La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
				ppm	ppm	%	ppm	%	ppm	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
				1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.01	0.1	0.01	0.05	1	0.5	
L108W 11200 N	Soil			9	15	0.26	99	0.010	2	1.80	0.005	0.05	0.2	0.12	3.2	0.2	<0.05	6	2.4
L108W 11250 N	Soil			10	8	0.05	53	0.007	<1	1.22	0.002	0.04	0.2	0.13	1.3	0.2	<0.05	7	1.1
L108W 11300 N	Soil			12	14	0.18	75	0.009	2	2.11	0.004	0.05	0.1	0.21	3.1	0.2	<0.05	5	1.9
L108W 11350 N	Soil			8	13	0.22	73	0.012	3	2.39	0.004	0.04	0.2	0.39	3.0	0.2	<0.05	7	1.9
L108W 11400 N	Soil			11	12	0.16	79	0.009	1	1.79	0.005	0.07	0.2	0.14	2.1	0.3	0.10	8	2.5
L108W 11450 N	Soil			11	13	0.20	101	0.006	<1	1.77	0.005	0.06	0.2	0.17	1.5	0.2	0.09	7	1.6
L108W 11500 N	Soil			22	2	0.33	264	0.005	1	1.96	0.008	0.07	0.1	0.24	1.6	0.3	0.28	5	1.6
L108W 11550 N	Soil			8	10	0.16	121	0.004	<1	1.18	0.004	0.06	0.1	0.09	1.3	0.2	0.07	6	0.6
L108W 11600 N	Soil			7	9	0.14	184	0.004	<1	1.52	0.005	0.05	0.1	0.20	2.5	0.2	<0.05	4	2.8
L108W 11650 N	Soil			6	28	0.37	98	0.006	<1	3.28	0.006	0.07	<0.1	0.16	4.7	0.3	<0.05	5	2.1
L108W 11700 N	Soil			13	13	0.17	96	0.018	<1	1.89	0.005	0.05	0.2	0.25	2.9	0.2	<0.05	8	5.5
L108W 11750 N	Soil			11	14	0.25	75	0.012	<1	2.14	0.004	0.05	0.1	0.28	2.3	0.3	<0.05	8	2.0
L108W 11800 N	Soil			9	10	0.16	230	0.005	<1	1.50	0.006	0.07	0.2	0.09	1.5	0.3	<0.05	7	1.1
L108W 11850 N	Soil			8	7	0.08	118	0.010	2	0.80	0.004	0.08	0.2	0.04	1.0	0.3	<0.05	7	<0.5
L108W 11900 N	Soil			9	5	0.03	27	0.004	2	0.72	0.002	0.05	<0.1	0.03	0.7	0.3	<0.05	6	<0.5
L108W 11950 N	Soil			10	11	0.20	133	0.009	2	1.49	0.005	0.06	0.1	0.16	1.3	0.2	0.06	6	1.2
L108W 12000 N	Soil			8	15	0.20	72	0.007	1	1.50	0.004	0.10	0.2	0.10	1.9	0.5	<0.05	8	2.0
L108W 12050 N	Soil			7	17	0.28	74	0.007	1	2.20	0.005	0.07	0.1	0.19	2.8	0.3	<0.05	6	2.3
L108W 12100 N	Soil			11	12	0.23	90	0.006	<1	2.27	0.005	0.06	0.1	0.25	1.9	0.4	<0.05	8	1.5
L108W 12150 N	Soil			8	13	0.18	50	0.007	2	2.06	0.004	0.05	0.2	0.17	2.2	0.3	<0.05	7	1.7
L108W 12200 N	Soil			6	11	0.20	57	0.013	2	1.85	0.005	0.05	0.2	0.18	1.9	0.2	<0.05	7	0.8
L108W 12250 N	Soil			9	14	0.15	241	0.014	2	1.39	0.005	0.07	<0.1	0.12	1.6	0.2	<0.05	8	0.9
L108W 12300 N	Soil			7	18	0.33	83	0.016	3	2.53	0.006	0.07	0.1	0.12	1.9	0.1	<0.05	7	<0.5
ZSP-08-044	Soil			17	12	0.24	310	0.007	3	1.30	0.013	0.08	0.1	0.15	4.5	0.3	<0.05	3	1.5
ZSP-08-045	Soil			6	23	0.28	58	0.021	2	2.47	0.006	0.06	0.1	0.11	3.6	0.2	<0.05	9	0.6
ZSP-08-046	Soil			5	14	0.13	48	0.012	3	1.45	0.004	0.06	0.1	0.10	2.5	0.2	<0.05	9	<0.5
ZSP-08-047	Soil			6	21	0.20	47	0.012	2	2.43	0.006	0.04	0.2	0.15	3.3	0.2	<0.05	10	0.9
ZSP-08-048	Soil			6	14	0.12	80	0.018	2	1.28	0.006	0.08	0.1	0.05	1.2	0.2	<0.05	8	<0.5
ZSP-08-049	Soil			6	19	0.22	57	0.013	2	2.10	0.005	0.06	<0.1	0.10	3.1	0.3	<0.05	10	0.6
ZSP-08-050	Soil			6	14	0.11	85	0.013	2	1.65	0.010	0.07	0.1	0.21	2.2	0.5	<0.05	8	<0.5

This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
 Report Date: August 19, 2008

Page: 3 of 3 Part 1

CERTIFICATE OF ANALYSIS

SMI08000664.1

Method	Analyte	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
		Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	P
Unit		ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	%
MDL		0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	0.001
ZSP-08-051	Soil	1.4	52.0	92.0	235	1.2	14.5	10.8	925	5.86	83.1	0.6	11.1	0.9	19	0.6	2.9	1.8	82	0.08	0.068
ZSP-08-052	Soil	1.5	44.8	74.6	310	0.6	13.0	7.3	525	4.92	46.2	0.8	16.6	1.3	13	0.9	1.9	0.9	75	0.05	0.074
ZSP-08-053	Soil	1.0	10.9	10.4	60	0.2	3.9	2.8	136	2.33	19.2	0.4	38.8	0.7	7	<0.1	1.4	0.6	62	<0.01	0.020
ZSP-08-054	Soil	1.5	28.1	101.5	213	0.5	9.6	5.5	634	5.26	47.8	0.6	10.8	1.5	10	0.4	1.6	1.0	65	0.03	0.106
ZSP-08-055	Soil	2.3	36.2	100.4	307	0.5	11.5	6.6	423	5.68	72.0	0.9	18.2	1.9	10	0.8	2.1	1.8	61	0.04	0.065
ZSP-08-056	Soil	1.7	27.8	70.8	133	0.4	5.6	3.2	298	3.57	40.6	0.7	13.0	0.2	11	0.5	1.4	1.1	61	0.05	0.049
ZSP-08-057	Soil	1.6	43.2	84.0	367	0.4	8.2	6.4	1416	3.78	48.2	0.7	5.4	0.2	30	1.6	2.0	0.7	68	0.53	0.081
ZSP-08-058	Soil	1.7	26.7	141.7	629	0.8	14.8	7.4	369	5.05	133.1	0.9	12.7	1.6	13	0.8	1.6	0.7	72	0.05	0.059
ZSP-08-059	Soil	1.7	47.9	72.5	125	0.8	12.2	4.6	248	5.22	56.6	0.8	11.4	0.4	14	0.3	2.0	1.0	76	0.07	0.047
ZSP-08-060	Soil	1.6	46.2	132.0	223	1.0	9.2	6.5	625	3.55	72.2	1.2	48.9	0.3	26	0.3	1.9	2.3	64	0.29	0.070
ZSP-08-061	Soil	1.3	28.9	64.5	100	1.6	6.2	3.9	342	3.53	54.0	0.7	10.3	0.2	8	0.5	2.0	1.0	84	0.04	0.061
ZSP-08-062	Soil	1.2	37.7	190.4	203	0.8	8.0	9.8	2499	3.82	51.3	0.7	15.3	0.2	10	0.4	1.8	2.0	61	0.06	0.145
ZSP-08-063	Soil	1.1	33.1	35.0	64	0.8	8.1	2.5	135	2.78	19.6	0.6	3.5	0.2	9	0.6	1.6	0.5	84	0.01	0.020
ZSP-08-064	Soil	1.4	21.9	36.2	78	0.2	7.2	3.8	340	3.98	28.9	0.7	5.0	0.2	6	0.2	1.3	0.4	75	0.01	0.037
ZSP-08-065	Soil	1.3	33.4	49.6	124	0.4	9.7	5.4	750	5.43	33.2	1.0	4.9	0.7	9	0.4	1.4	0.4	90	0.02	0.126
ZSP-08-066	Soil	1.3	50.7	64.9	197	0.3	19.8	9.0	646	5.12	47.3	1.0	137.3	2.7	10	0.4	1.7	0.5	74	0.05	0.048
ZSP-08-067	Soil	3.0	20.4	28.1	133	1.2	6.4	5.4	1023	3.69	24.2	0.7	3.3	1.3	7	0.2	2.0	0.3	52	0.03	0.085
ZSP-08-068	Soil	1.8	39.9	47.7	288	1.1	17.5	6.7	633	4.18	43.1	1.6	6.6	1.8	12	0.9	2.0	0.4	56	0.06	0.099
ZSP-08-069	Soil	1.7	45.9	75.5	225	0.3	23.1	14.6	1354	4.43	47.0	2.8	10.3	2.9	27	0.8	2.3	0.6	64	0.26	0.074
ZSP-08-070	Soil	6.2	108.6	109.4	263	3.3	18.8	14.5	9177	3.21	44.7	6.8	22.6	0.8	97	6.0	2.7	1.6	41	1.07	0.231
ZSP-08-071	Soil	2.6	46.5	77.7	153	0.2	12.7	4.6	280	1.35	16.5	1.0	6.5	0.4	33	0.3	2.5	0.6	73	0.26	0.139
ZSP-08-072	Soil	1.5	31.8	75.9	101	0.3	8.8	4.2	250	5.23	62.1	0.8	6.4	1.6	9	0.2	1.9	0.9	88	0.02	0.213
ZSP-08-073	Soil	1.8	42.4	63.1	203	0.3	20.1	11.6	793	4.19	46.7	1.7	16.3	1.3	18	0.2	2.1	0.5	63	0.08	0.078
ZSP-08-074	Soil	1.7	20.6	59.0	136	1.1	8.8	5.7	346	4.82	38.8	0.6	9.8	1.6	8	0.2	1.7	0.8	92	0.01	0.040



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
 Report Date: August 19, 2008

Page: 3 of 3 Part 2

CERTIFICATE OF ANALYSIS

SMI08000664.1

Method	Analyte	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
		La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
Unit		ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm
MDL		1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.05	1	0.5	
ZSP-08-051	Soil	6	19	0.31	123	0.011	3	1.87	0.006	0.07	0.1	0.15	3.7	0.2	<0.05	7	0.6
ZSP-08-052	Soil	7	17	0.21	97	0.011	3	2.40	0.006	0.06	0.1	0.17	3.3	0.2	<0.05	7	<0.5
ZSP-08-053	Soil	10	6	0.04	30	0.008	4	0.71	0.004	0.03	0.1	0.02	1.3	0.3	<0.05	5	<0.5
ZSP-08-054	Soil	7	15	0.18	61	0.008	3	1.92	0.005	0.06	0.1	0.13	2.5	0.3	<0.05	7	<0.5
ZSP-08-055	Soil	6	13	0.19	75	0.011	3	3.57	0.006	0.05	0.2	0.21	3.2	0.2	<0.05	6	0.9
ZSP-08-056	Soil	8	8	0.08	72	0.015	2	1.25	0.004	0.05	0.2	0.10	1.2	0.2	<0.05	6	<0.5
ZSP-08-057	Soil	8	12	0.10	109	0.011	2	0.97	0.005	0.07	0.2	0.08	1.5	0.1	<0.05	5	0.5
ZSP-08-058	Soil	6	17	0.25	108	0.006	2	2.84	0.005	0.06	0.1	0.19	3.7	0.2	<0.05	6	0.7
ZSP-08-059	Soil	7	12	0.13	98	0.014	4	1.42	0.004	0.06	0.1	0.18	2.1	0.3	<0.05	8	<0.5
ZSP-08-060	Soil	13	10	0.12	139	0.007	2	0.88	0.005	0.09	<0.1	0.09	1.2	0.2	<0.05	5	0.5
ZSP-08-061	Soil	6	6	0.09	53	0.014	5	0.81	0.003	0.04	0.2	0.09	1.0	0.2	0.06	8	<0.5
ZSP-08-062	Soil	7	8	0.07	81	0.009	3	0.87	0.003	0.06	0.1	0.10	0.9	0.3	0.05	4	<0.5
ZSP-08-063	Soil	6	12	0.03	95	0.013	3	0.54	0.003	0.03	0.1	0.03	0.7	0.1	<0.05	4	<0.5
ZSP-08-064	Soil	5	7	0.10	54	0.010	2	1.06	0.003	0.02	0.2	0.06	1.1	0.1	<0.05	6	<0.5
ZSP-08-065	Soil	7	13	0.14	88	0.017	3	1.75	0.005	0.03	0.1	0.10	1.8	0.2	<0.05	11	<0.5
ZSP-08-066	Soil	5	22	0.31	102	0.004	4	2.75	0.005	0.06	0.2	0.12	3.7	0.2	<0.05	7	<0.5
ZSP-08-067	Soil	7	6	0.08	108	0.003	2	1.74	0.003	0.05	0.2	0.15	2.6	0.3	<0.05	5	<0.5
ZSP-08-068	Soil	10	8	0.19	186	0.004	1	2.53	0.005	0.04	0.4	0.15	3.7	0.2	<0.05	5	<0.5
ZSP-08-069	Soil	16	14	0.28	163	0.007	3	2.62	0.007	0.05	0.2	0.16	6.6	0.3	<0.05	5	0.6
ZSP-08-070	Soil	62	4	0.20	418	0.014	3	1.71	0.010	0.05	0.3	0.32	6.5	0.5	0.11	5	1.3
ZSP-08-071	Soil	7	13	0.23	163	0.008	2	1.80	0.007	0.04	0.1	0.09	1.9	0.2	<0.05	5	0.7
ZSP-08-072	Soil	6	12	0.10	57	0.013	3	1.40	0.003	0.04	0.1	0.14	2.5	0.2	<0.05	9	<0.5
ZSP-08-073	Soil	10	16	0.29	121	0.009	2	1.91	0.005	0.07	0.1	0.13	3.8	0.2	<0.05	4	<0.5
ZSP-08-074	Soil	7	12	0.09	55	0.016	3	1.10	0.003	0.04	0.2	0.17	2.4	0.1	<0.05	9	<0.5

QUALITY CONTROL REPORT

SMI08000664.1

Method	Analyte	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
		Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	P
Unit		ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	%
MDL		0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	0.001
Pulp Duplicates																					
L108W 12150 N	Soil	2.8	59.3	68.2	80	0.8	6.7	4.1	206	6.76	32.1	1.1	14.5	1.1	7	0.4	1.2	1.7	81	0.03	0.074
REP L108W 12150 N	QC	2.8	58.2	66.9	80	0.8	6.6	4.1	211	6.86	30.9	1.1	16.7	1.1	7	0.3	1.2	1.6	80	0.03	0.077
ZSP-08-059	Soil	1.7	47.9	72.5	125	0.8	12.2	4.6	248	5.22	56.6	0.8	11.4	0.4	14	0.3	2.0	1.0	76	0.07	0.047
REP ZSP-08-059	QC	1.8	48.4	73.9	125	0.9	11.8	4.4	255	5.28	56.4	0.8	10.5	0.4	15	0.3	1.9	0.9	76	0.07	0.048
ZSP-08-062	Soil	1.2	37.7	190.4	203	0.8	8.0	9.8	2499	3.82	51.3	0.7	15.3	0.2	10	0.4	1.8	2.0	61	0.06	0.145
REP ZSP-08-062	QC	1.5	38.6	195.2	216	0.9	9.0	9.6	2603	3.83	51.7	0.8	9.4	0.2	10	0.5	1.9	2.1	64	0.06	0.157
Reference Materials																					
STD DS7	Standard	20.6	109.1	77.5	399	0.9	56.3	9.7	596	2.38	50.6	5.3	70.4	4.4	69	6.0	5.9	4.7	88	0.89	0.073
STD DS7	Standard	20.7	116.7	62.1	408	0.8	54.9	9.7	661	2.44	52.1	4.5	63.1	4.3	76	5.8	5.4	4.1	85	0.98	0.074
STD DS7	Standard	20.8	112.7	77.7	407	0.8	56.5	9.4	630	2.38	51.9	5.2	75.3	4.5	72	6.2	6.3	4.9	90	0.90	0.077
STD DS7 Expected		20.9	109	70.6	411	0.9	56	9.7	627	2.39	48.2	4.9	70	4.4	69	6.4	5.9	4.5	86	0.93	0.08
BLK	Blank	<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01	<0.001
BLK	Blank	<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01	<0.001
BLK	Blank	<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01	<0.001

QUALITY CONTROL REPORT

SMI08000664.1

Method	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
Analyte	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se	
Unit	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
MDL	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5	
Pulp Duplicates																	
L108W 12150 N	Soil	8	13	0.18	50	0.007	2	2.06	0.004	0.05	0.2	0.17	2.2	0.3	<0.05	7	1.7
REP L108W 12150 N	QC	8	13	0.18	51	0.007	<1	1.95	0.004	0.04	0.1	0.17	2.2	0.3	<0.05	7	1.9
ZSP-08-059	Soil	7	12	0.13	98	0.014	4	1.42	0.004	0.06	0.1	0.18	2.1	0.3	<0.05	8	<0.5
REP ZSP-08-059	QC	7	11	0.13	102	0.010	3	1.39	0.004	0.06	0.2	0.16	2.1	0.3	<0.05	7	0.8
ZSP-08-062	Soil	7	8	0.07	81	0.009	3	0.87	0.003	0.06	0.1	0.10	0.9	0.3	0.05	4	<0.5
REP ZSP-08-062	QC	7	8	0.07	86	0.007	3	0.92	0.003	0.06	0.1	0.10	0.8	0.3	<0.05	5	<0.5
Reference Materials																	
STD DS7	Standard	12	198	1.06	378	0.121	36	1.01	0.087	0.44	3.6	0.22	2.6	4.2	0.24	5	3.3
STD DS7	Standard	15	205	1.02	400	0.126	38	1.10	0.103	0.47	3.8	0.21	2.8	4.1	0.16	5	2.5
STD DS7	Standard	12	205	1.03	377	0.120	38	1.00	0.092	0.46	4.1	0.19	2.6	4.4	0.21	5	3.7
STD DS7 Expected		13	163	1.05	370	0.124	39	0.959	0.073	0.44	3.8	0.2	2.5	4.2	0.21	5	3.5
BLK	Blank	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
BLK	Blank	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
BLK	Blank	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.

Vancouver BC V6C 1Z7 Canada

Submitted By:

Glen Garratt

Receiving Lab:

Canada-Smithers

Received:

August 05, 2008

Report Date:

August 28, 2008

Page:

1 of 8

CERTIFICATE OF ANALYSIS

SMI08000686.1

CLIENT JOB INFORMATION

Project: Zymo
Shipment ID: zy-so-08-03
P.O. Number
Number of Samples: 186

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
DISP-RJT-SOIL Immediate Disposal of Soil Reject

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Mincord Exploration Consultants Ltd.
110 - 325 Howe St.
Vancouver BC V6C 1Z7
Canada

CC: Bob Johnston

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status
SS80	186	Dry at 60C sieve 100g to -80 mesh		
Dry at 60C	186	Dry at 60C		
1DX15	179	1:1:1 Aqua Regia digestion ICP-MS analysis	15	Completed

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only. All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.

Vancouver BC V6C 1Z7 Canada

Submitted By:

Glen Garratt

Receiving Lab:

Canada-Smithers

Received:

August 06, 2008

Report Date:

September 02, 2008

Page:

1 of 2

CERTIFICATE OF ANALYSIS

SMI08000697.1

CLIENT JOB INFORMATION

Project: Zymo
Shipment ID: zy-rk-08-09
P.O. Number
Number of Samples: 16

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
DISP-RJT Dispose of Reject After 90 days

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Mincord Exploration Consultants Ltd.
110 - 325 Howe St.
Vancouver BC V6C 1Z7
Canada

CC: Bob Johnston

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status
R150	16	Crush, split and pulverize rock to 200 mesh		
1DX15	16	1:1:1 Aqua Regia digestion ICP-MS analysis	15	Completed

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only. All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.



AcmeLabs ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
Report Date: September 02, 2008

Page: 2 of 2 **Part** 1

CERTIFICATE OF ANALYSIS

SMI08000697.1

Method	Analyte	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
Unit	MDL	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	
		0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01
726668	Rock	1.61	2.2	1330	160.4	80	1.2	85.3	271.2	602	20.64	188.8	0.3	33.5	0.6	15	0.3	7.5	5.5	110	1.82	
726669	Rock	2.04	1.7	16.9	21.3	99	0.1	6.8	4.7	961	1.93	2.6	7.0	<0.5	12.5	49	0.2	0.4	0.2	30	1.03	
726670	Rock	1.83	1.0	36.0	7.0	48	<0.1	7.9	5.1	223	2.49	7.5	<0.1	1.2	1.2	36	0.2	0.7	<0.1	95	0.26	
726671	Rock	2.36	24.7	4351	8.9	76	2.0	20.7	23.3	615	14.57	5.8	1.1	425.6	2.7	13	0.2	0.3	0.3	134	0.72	
726672	Rock	2.94	5.2	3349	7.4	44	1.5	6.4	8.5	245	7.73	6.1	1.3	534.4	9.2	33	0.1	1.3	0.4	51	0.08	
726673	Rock	1.91	31.5	1861	8.4	39	1.2	5.2	9.4	238	8.01	13.0	1.0	665.9	9.0	25	<0.1	21.2	0.4	57	0.06	
726674	Rock	2.86	19.5	8607	9.5	61	4.1	5.4	12.6	492	8.66	21.6	1.5	647.0	9.9	30	0.2	1.4	0.4	55	0.29	
726675	Rock	2.44	22.0	4380	10.0	49	1.8	5.4	11.7	332	8.13	2.3	1.4	587.7	11.3	29	0.1	0.6	0.3	70	0.21	
726676	Rock	2.40	7.5	1430	38.0	115	0.5	5.1	7.8	609	3.04	7.2	3.6	136.9	15.5	92	0.6	0.7	0.2	61	0.93	
726677	Rock	2.96	2.2	4306	7.6	50	1.7	4.0	10.6	366	5.45	7.5	2.4	478.8	16.1	55	0.2	0.6	0.3	75	0.32	
726678	Rock	2.19	2.3	695.3	14.1	52	0.5	3.7	5.4	505	3.49	103.8	5.4	108.0	15.6	66	0.1	2.2	0.3	28	0.34	
726679	Rock	1.71	1.7	1034	36.5	106	0.9	5.0	5.7	834	2.61	33.5	5.5	21.9	17.3	331	0.6	4.0	<0.1	18	0.49	
726680	Rock	2.51	4.4	1886	11.6	62	0.8	5.5	10.1	795	6.01	81.5	2.6	286.3	16.0	80	0.1	6.6	0.3	74	0.24	
726681	Rock	3.09	1.8	2988	8.6	84	0.6	3.8	10.2	651	5.33	4.1	3.4	263.0	15.8	424	0.2	0.3	0.2	69	1.48	
726682	Rock	2.67	4.3	50.8	40.5	150	<0.1	3.7	9.2	1423	2.71	137.9	6.6	5.1	9.7	202	0.3	1.8	0.2	33	2.03	
830962	Rock	0.82	2.7	579.3	4.1	41	0.2	5.6	10.3	272	5.52	7.5	0.9	43.5	4.7	207	<0.1	0.2	0.1	126	1.33	



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.

Vancouver BC V6C 1Z7 Canada

Project:

Zymo

Report Date:

September 02, 2008

Page:

2 of 2

Part 2

CERTIFICATE OF ANALYSIS

SMI08000697.1

Method	Analyte	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
		P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
Unit		%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm
MDL		0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.01	0.1	0.01	0.1	0.05	1	0.5
726668	Rock	0.779	15	13	1.21	11	0.007	3	3.46	0.012	0.01	<0.1	0.13	14.0	0.1	>10	11	17.1
726669	Rock	0.094	24	10	0.36	312	0.003	4	0.72	0.046	0.21	0.2	0.07	2.2	0.1	0.11	4	<0.5
726670	Rock	0.063	5	13	0.42	69	<0.001	2	1.71	0.048	0.19	<0.1	0.01	6.4	0.4	0.07	5	<0.5
726671	Rock	0.287	20	15	0.89	133	0.036	2	1.42	0.041	0.32	0.1	0.50	6.7	0.3	0.57	11	3.5
726672	Rock	0.060	5	13	0.07	325	0.002	3	0.36	0.019	0.24	0.1	0.69	2.2	0.1	0.36	4	4.0
726673	Rock	0.069	7	9	0.03	220	0.002	2	0.33	0.014	0.21	0.2	0.19	2.2	0.1	0.19	4	4.5
726674	Rock	0.065	6	12	0.19	141	0.001	4	0.40	0.015	0.27	<0.1	0.52	2.5	0.2	0.75	3	6.3
726675	Rock	0.078	7	12	0.15	217	0.003	2	0.33	0.019	0.21	0.1	0.53	2.8	0.1	0.44	5	4.1
726676	Rock	0.142	27	11	0.26	568	0.026	2	0.56	0.056	0.22	0.1	0.82	5.3	0.2	0.17	3	1.1
726677	Rock	0.101	12	10	0.14	398	0.004	3	0.54	0.031	0.27	0.1	0.44	3.4	0.1	0.37	4	4.2
726678	Rock	0.104	27	7	0.08	724	0.002	4	0.70	0.043	0.36	<0.1	0.27	3.9	0.3	0.14	1	0.5
726679	Rock	0.099	23	6	0.06	1454	0.002	4	0.86	0.026	0.35	<0.1	0.92	4.1	0.2	0.09	1	<0.5
726680	Rock	0.112	14	10	0.17	938	0.002	3	0.76	0.032	0.29	<0.1	0.75	4.0	0.2	0.14	4	2.5
726681	Rock	0.152	26	7	0.33	430	0.004	3	0.91	0.059	0.30	<0.1	0.58	6.0	0.1	0.23	5	2.3
726682	Rock	0.155	31	4	0.21	1630	0.003	4	0.81	0.026	0.42	<0.1	0.49	4.5	0.3	0.07	1	0.6
830962	Rock	0.192	7	6	1.83	73	0.213	2	3.27	0.228	0.17	<0.1	<0.01	6.9	0.3	0.75	11	1.0

QUALITY CONTROL REPORT

SMI08000697.1

Method	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
Unit	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	ppm	
MDL	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	
Pulp Duplicates																					
726679	Rock	1.71	1.7	1034	36.5	106	0.9	5.0	5.7	834	2.61	33.5	5.5	21.9	17.3	331	0.6	4.0	<0.1	18	0.49
REP 726679	QC		1.7	1028	36.0	103	0.8	4.6	5.8	831	2.55	33.3	5.3	33.3	17.8	316	0.5	3.6	<0.1	17	0.48
Reference Materials																					
STD DS7	Standard		18.5	113.5	74.9	403	0.8	54.6	9.9	670	2.51	49.1	5.3	82.4	4.5	68	6.0	6.1	4.8	86	0.90
STD DS7	Standard		21.7	121.7	78.4	409	0.9	58.6	9.8	673	2.54	50.2	5.7	68.9	4.8	78	6.3	6.3	4.8	88	0.95
STD DS7	Standard		19.8	111.1	76.5	418	0.8	56.5	9.5	633	2.41	50.4	5.5	68.8	4.9	79	6.0	6.2	4.8	85	0.95
STD DS7	Standard		20.1	113.0	81.0	415	0.8	57.0	9.9	664	2.43	52.1	6.0	65.1	5.3	85	6.3	6.0	5.0	89	1.01
STD DS7 Expected			20.9	109	70.6	411	0.9	56	9.7	627	2.39	48.2	4.9	70	4.4	69	6.4	5.9	4.5	86	0.93
BLK	Blank		<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01
BLK	Blank		<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01
Prep Wash																					
G1	Prep Blank	<0.01	1.2	2.8	4.0	52	<0.1	11.3	4.7	598	2.06	<0.5	3.4	<0.5	5.9	84	<0.1	<0.1	0.1	40	0.67
G1	Prep Blank	<0.01	1.1	2.4	3.4	50	<0.1	9.5	4.9	601	2.04	<0.5	3.3	<0.5	5.4	76	<0.1	<0.1	<0.1	39	0.56

QUALITY CONTROL REPORT

SMI08000697.1

Method		1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte		P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
Unit		%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm
MDL		0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5
Pulp Duplicates																		
726679	Rock	0.099	23	6	0.06	1454	0.002	4	0.86	0.026	0.35	<0.1	0.92	4.1	0.2	0.09	1	<0.5
REP 726679	QC	0.095	22	6	0.06	1194	0.002	5	0.92	0.023	0.34	<0.1	0.88	3.8	0.3	0.08	1	0.7
Reference Materials																		
STD DS7	Standard	0.074	12	161	1.07	382	0.125	40	1.04	0.076	0.50	3.9	0.20	2.3	4.1	0.19	5	3.8
STD DS7	Standard	0.073	13	168	1.10	420	0.139	39	1.10	0.087	0.51	4.0	0.21	2.6	4.4	0.19	5	3.4
STD DS7	Standard	0.075	14	172	1.04	370	0.126	42	1.03	0.085	0.45	3.9	0.20	2.5	4.1	0.19	5	3.8
STD DS7	Standard	0.076	15	185	1.10	393	0.133	39	1.10	0.090	0.46	3.7	0.22	2.5	4.5	0.19	5	3.4
STD DS7 Expected		0.08	13	163	1.05	370	0.124	39	0.959	0.073	0.44	3.8	0.2	2.5	4.2	0.21	4.6	3.5
BLK	Blank	<0.001	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
BLK	Blank	<0.001	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
Prep Wash																		
G1	Prep Blank	0.078	11	20	0.67	233	0.136	2	1.31	0.120	0.59	0.4	<0.01	3.6	0.4	<0.05	6	<0.5
G1	Prep Blank	0.071	10	17	0.65	231	0.127	2	1.17	0.092	0.57	0.4	<0.01	3.0	0.4	0.06	5	<0.5



AcmeLabs ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
Report Date: August 28, 2008

Page: 2 of 8 **Part** 1

CERTIFICATE OF ANALYSIS

SMI08000686.1

Method	Analyte	Unit	MDL	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15		
				Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	P
				ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	
				0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	0.001
L88W	105 50 N	Soil		2.7	48.2	28.4	88	0.4	14.1	6.3	382	4.98	38.7	1.5	4.8	0.4	10	0.3	2.2	0.3	80	0.02	0.065
L88W	106 00 N	Soil		2.3	122.5	28.9	103	2.2	18.1	7.1	258	4.47	36.2	3.3	5.0	0.1	13	0.3	1.9	0.3	83	0.03	0.093
L88W	106 50 N	Soil		1.7	40.2	40.5	68	0.6	10.0	5.0	276	5.94	42.5	0.7	7.8	0.7	6	0.1	2.2	0.7	100	<0.01	0.060
L88W	107 00 N	Soil		1.3	279.8	39.6	71	4.2	5.1	2.8	190	2.62	13.0	3.3	6.7	0.4	8	0.5	0.7	0.4	52	0.02	0.083
L88W	108 00 N	Soil		1.3	27.8	26.3	66	0.8	9.9	4.4	216	4.83	30.2	0.5	5.4	0.6	13	0.4	2.5	0.2	92	0.02	0.050
L88W	108 50 N	Soil		1.9	44.0	48.3	117	1.0	17.4	10.6	704	5.48	41.0	0.8	6.5	1.2	15	0.4	3.0	0.3	78	0.06	0.117
L88W	109 00 N	Soil		2.0	60.5	38.3	153	0.2	21.5	15.3	905	4.95	37.1	1.1	9.9	0.9	17	0.3	2.9	0.3	87	0.08	0.076
L88W	109 50 N	Soil		5.7	36.1	32.0	47	0.8	3.2	2.2	240	3.39	26.3	0.8	59.9	0.4	9	0.1	1.3	1.1	60	0.01	0.057
L88W	110 00 N	Soil		I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.
L88W	110 50 N	Soil		2.6	35.9	33.6	93	0.5	9.1	6.0	460	4.60	27.8	1.2	5.2	0.5	11	0.3	2.1	0.4	79	0.05	0.090
L88W	111 00 N	Soil		2.7	35.4	57.6	117	0.4	22.8	12.1	982	5.06	25.0	1.3	4.2	0.4	12	0.2	1.6	0.5	122	0.07	0.105
L88W	111 50 N	Soil		3.5	52.3	43.5	101	0.2	10.2	5.9	444	4.99	27.5	1.4	8.5	0.3	12	0.2	1.9	0.5	85	0.07	0.127
L88W	112 00 N	Soil		4.8	55.5	49.9	76	0.3	5.9	4.5	316	7.17	36.1	1.1	7.7	1.3	5	0.3	3.2	0.9	77	0.01	0.080
L88W	112 50 N	Soil		3.3	112.5	58.1	168	0.4	10.5	17.6	1313	5.72	31.0	1.9	33.8	3.3	13	0.4	3.5	0.9	59	0.06	0.195
L88W	113 00 N	Soil		2.9	54.8	53.3	109	0.2	8.9	7.0	522	5.22	27.5	1.1	8.7	1.1	7	0.1	2.1	0.7	83	0.03	0.057
L88W	113 50 N	Soil		3.8	52.9	37.5	80	0.4	4.9	4.7	369	3.59	18.8	1.6	11.9	0.1	238	0.4	1.3	0.6	64	0.42	0.070
L88W	114 00 N	Soil		1.9	45.3	39.6	86	0.4	5.5	4.8	564	3.29	25.0	1.1	5.0	0.1	151	0.3	1.9	0.7	68	0.39	0.088
L88W	114 50 N	Soil		2.0	39.6	28.8	96	0.3	6.4	4.2	299	3.49	23.4	1.0	4.4	0.2	24	0.1	2.6	0.6	84	0.09	0.048
L88W	115 00 N	Soil		3.7	48.4	55.8	102	0.1	6.7	6.9	984	4.18	26.1	1.2	8.3	0.3	23	0.2	2.5	0.6	70	0.10	0.105
L88W	115 50 N	Soil		2.4	64.0	88.8	150	0.9	9.5	7.1	772	6.15	36.3	1.7	24.7	0.8	11	0.2	2.5	1.2	95	0.06	0.319
L88W	116 00 N	Soil		2.0	78.7	228.1	157	3.3	6.6	6.7	1428	6.20	58.8	2.1	70.9	0.9	9	0.4	2.3	5.4	65	0.04	0.332
L88W	116 50 N	Soil		1.9	36.8	58.8	260	1.0	2.4	3.7	384	2.78	56.7	0.8	9.2	1.2	3	0.1	1.1	2.0	68	<0.01	0.051
L88W	117 00 N	Soil		1.3	55.4	75.7	1001	2.0	20.4	13.4	4690	3.77	20.7	2.5	10.4	0.6	39	4.3	1.5	0.5	74	0.29	0.079
L88W	117 50 N	Soil		2.7	43.8	103.8	283	1.3	7.2	7.7	3510	4.11	28.5	2.1	13.6	0.9	23	1.4	1.3	1.0	66	0.08	0.120
L88W	118 00 N	Soil		1.3	35.1	58.1	107	0.2	12.4	6.5	513	4.86	25.7	1.3	5.9	0.3	21	0.4	2.0	0.3	122	0.09	0.066
L88W	118 50 N	Soil		2.2	66.3	140.9	302	1.1	11.6	8.9	1675	4.32	32.4	2.7	16.2	0.8	27	1.0	1.6	1.7	65	0.10	0.123
L88W	119 00 N	Soil		1.6	37.9	80.0	138	0.5	12.5	7.2	611	4.78	32.9	1.6	11.1	0.2	17	0.4	2.4	0.8	108	0.05	0.051
L88W	119 50 N	Soil		1.7	32.4	223.7	165	0.5	8.6	8.4	1302	5.80	36.0	1.6	10.0	0.6	15	0.3	2.2	1.6	76	0.12	0.189
L88W	120 00 N	Soil		1.7	38.1	315.2	161	1.5	10.4	7.4	2259	3.67	22.5	3.1	5.6	0.2	25	0.6	1.2	0.8	73	0.08	0.120
L88W	120 50 N	Soil		7.3	47.6	81.8	120	0.7	11.0	7.9	672	5.15	23.8	2.4	3.5	0.6	19	0.5	2.0	0.9	103	0.09	0.079

This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.



AcmeLabs ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
Report Date: August 28, 2008

Page: 2 of 8 **Part** 2

CERTIFICATE OF ANALYSIS

SMI08000686.1

Method	Analyte	Unit	MDL	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15		
				La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
				ppm	ppm	%	ppm	%	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm		
				1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.01	0.01	0.05	1	0.5		
L88W	105 50 N	Soil		8	21	0.24	74	0.008	<1	2.45	0.005	0.06	0.1	0.18	3.2	0.2	<0.05	9	1.0
L88W	106 00 N	Soil		9	27	0.38	85	0.012	2	2.23	0.007	0.11	0.1	0.23	2.2	0.2	0.05	9	0.5
L88W	106 50 N	Soil		4	20	0.15	53	0.010	<1	1.74	0.004	0.05	0.2	0.10	2.8	0.2	<0.05	10	<0.5
L88W	107 00 N	Soil		11	15	0.10	40	0.007	<1	2.13	0.005	0.05	0.1	0.26	2.0	0.2	<0.05	7	0.6
L88W	108 00 N	Soil		4	21	0.16	95	0.012	<1	1.47	0.005	0.07	0.2	0.11	2.7	0.1	<0.05	9	0.7
L88W	108 50 N	Soil		5	25	0.26	80	0.007	2	2.43	0.005	0.06	0.1	0.15	3.8	0.2	<0.05	7	0.5
L88W	109 00 N	Soil		5	24	0.28	78	0.017	3	2.18	0.006	0.06	<0.1	0.12	4.2	0.2	<0.05	5	1.3
L88W	109 50 N	Soil		6	10	0.06	58	0.011	2	0.94	0.004	0.04	0.2	0.07	1.0	0.2	0.09	6	0.6
L88W	110 00 N	Soil		I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.
L88W	110 50 N	Soil		7	17	0.24	63	0.015	4	1.53	0.005	0.04	0.2	0.10	2.5	0.2	0.09	6	0.7
L88W	111 00 N	Soil		6	24	0.74	75	0.036	3	1.40	0.006	0.05	0.1	0.07	2.0	0.2	0.09	9	<0.5
L88W	111 50 N	Soil		7	16	0.25	78	0.010	4	1.81	0.004	0.05	0.2	0.11	1.6	0.3	0.06	7	<0.5
L88W	112 00 N	Soil		7	10	0.14	65	0.005	3	1.68	0.003	0.04	0.2	0.11	1.7	0.4	0.12	9	1.3
L88W	112 50 N	Soil		12	13	0.23	77	0.007	3	3.07	0.006	0.04	0.2	0.17	3.8	0.2	0.05	4	1.8
L88W	113 00 N	Soil		7	15	0.23	68	0.010	3	1.95	0.004	0.04	0.2	0.09	2.2	0.2	0.06	6	0.9
L88W	113 50 N	Soil		14	8	0.09	211	0.006	3	0.98	0.004	0.05	0.2	0.06	0.9	0.2	0.09	6	0.7
L88W	114 00 N	Soil		7	10	0.14	296	0.006	2	1.07	0.005	0.06	0.1	0.06	0.6	0.2	0.07	5	<0.5
L88W	114 50 N	Soil		9	10	0.11	104	0.010	2	1.00	0.004	0.06	0.2	0.08	1.1	0.3	<0.05	6	<0.5
L88W	115 00 N	Soil		8	11	0.14	101	0.008	3	0.98	0.005	0.06	0.2	0.05	1.2	0.2	0.07	5	0.6
L88W	115 50 N	Soil		8	17	0.22	56	0.013	2	2.13	0.003	0.06	0.2	0.15	2.7	0.2	0.05	10	0.7
L88W	116 00 N	Soil		5	11	0.15	79	0.007	2	1.46	0.004	0.05	0.2	0.22	1.9	0.3	0.11	5	1.3
L88W	116 50 N	Soil		2	4	0.02	46	0.002	6	1.01	0.007	0.04	0.1	0.02	2.8	0.5	0.10	4	<0.5
L88W	117 00 N	Soil		9	17	0.47	367	0.009	3	1.77	0.008	0.07	0.1	0.08	3.6	0.3	<0.05	6	0.7
L88W	117 50 N	Soil		14	13	0.17	149	0.004	3	2.20	0.005	0.05	0.1	0.16	2.3	0.3	0.10	6	0.9
L88W	118 00 N	Soil		6	20	0.25	140	0.039	4	1.61	0.006	0.09	0.2	0.08	2.5	0.2	<0.05	10	<0.5
L88W	118 50 N	Soil		20	15	0.24	157	0.005	3	2.13	0.005	0.06	0.2	0.15	2.7	0.3	0.07	5	1.2
L88W	119 00 N	Soil		6	18	0.29	92	0.016	3	1.61	0.005	0.06	0.1	0.08	1.7	0.2	<0.05	8	<0.5
L88W	119 50 N	Soil		11	15	0.18	56	0.009	3	1.38	0.004	0.07	0.2	0.05	1.6	0.2	0.08	7	0.8
L88W	120 00 N	Soil		12	16	0.24	211	0.008	3	1.83	0.006	0.08	<0.1	1.27	1.1	0.2	0.07	7	0.7
L88W	120 50 N	Soil		12	17	0.26	88	0.031	3	1.28	0.004	0.06	0.1	0.12	2.5	0.2	<0.05	9	1.0

This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.



AcmeLabs ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
Report Date: August 28, 2008

Page: 3 of 8 **Part** 1

CERTIFICATE OF ANALYSIS

SMI08000686.1

Method	Analyte	Unit	MDL	1DX15 Mo	1DX15 Cu	1DX15 Pb	1DX15 Zn	1DX15 Ag	1DX15 Ni	1DX15 Co	1DX15 Mn	1DX15 Fe	1DX15 As	1DX15 U	1DX15 Au	1DX15 Th	1DX15 Sr	1DX15 Cd	1DX15 Sb	1DX15 Bi	1DX15 V	1DX15 Ca	1DX15 P
				ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	%
				0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	0.001
L88W	121 00 N	Soil		1.2	31.3	58.7	85	0.3	12.3	8.6	930	4.43	24.0	1.0	5.3	0.3	16	0.3	1.7	0.7	90	0.10	0.224
L88W	121 50 N	Soil		1.6	44.3	36.6	312	1.6	18.4	10.8	2015	3.49	16.1	6.7	6.5	0.4	44	0.5	1.1	0.5	65	0.19	0.185
L88W	122 50 N	Soil		1.2	19.4	18.4	87	0.2	12.3	6.3	338	4.17	18.0	0.9	2.4	0.7	24	0.2	1.1	0.2	85	0.10	0.039
L88W	123 00 N	Soil		1.1	26.2	23.9	130	0.4	13.8	6.7	423	3.85	17.6	0.7	2.1	0.7	16	0.3	1.6	0.3	80	0.08	0.098
L88W	123 50 N	Soil		1.1	27.8	19.8	115	0.5	12.9	6.7	622	3.47	14.5	0.9	1.7	0.5	20	0.4	1.1	0.2	72	0.08	0.067
L88W	124 00 N	Soil		0.9	44.8	21.1	125	0.2	20.2	10.0	964	3.59	17.4	1.2	4.2	0.5	26	0.2	1.0	0.3	76	0.13	0.059
L88W	124 50 N	Soil		1.1	28.1	51.4	149	0.2	20.2	9.8	740	3.86	20.6	0.8	3.1	0.9	13	0.4	1.1	0.3	73	0.08	0.094
L90W	105 00 N	Soil		1.7	55.4	50.3	164	0.7	12.9	9.0	743	4.71	42.2	1.2	3.7	0.1	31	0.9	2.6	0.6	86	0.12	0.082
L90W	105 50 N	Soil		0.5	116.6	58.1	142	1.8	7.1	3.1	108	0.92	11.9	3.8	11.6	0.1	35	0.4	0.7	1.7	24	0.14	0.080
L90W	106 00 N	Soil		2.7	58.5	60.3	68	1.1	6.8	3.4	201	6.01	50.1	0.9	40.3	1.1	9	0.5	6.1	2.6	88	0.02	0.138
L90W	106 50 N	Soil		3.2	58.0	27.4	62	0.5	9.4	4.2	215	5.22	62.5	0.5	10.0	1.0	10	0.2	3.9	0.4	77	0.02	0.086
L90W	107 00 N	Soil		2.0	28.4	43.6	69	1.1	9.7	5.0	449	6.83	49.8	0.5	8.0	0.6	8	0.1	2.6	0.4	106	0.02	0.111
L90W	107 50 N	Soil		2.0	26.7	86.3	77	4.9	7.6	4.3	384	6.12	34.3	0.7	8.5	1.2	7	0.2	2.0	0.6	89	0.02	0.125
L90W	108 00 N	Soil		2.0	24.4	29.1	48	0.7	6.7	3.8	209	5.75	27.9	0.7	24.4	0.7	12	<0.1	2.1	0.4	121	0.01	0.063
L90W	108 50 N	Soil		6.4	115.9	8.1	34	0.3	3.2	2.8	114	2.14	7.6	1.2	27.8	0.5	6	<0.1	0.5	0.2	51	0.01	0.058
L90W	109 00 N	Soil		1.7	286.2	20.4	49	0.5	6.3	3.2	195	3.14	14.2	0.8	6.9	0.4	7	0.1	0.8	0.4	72	0.01	0.057
L90W	109 50 N	Soil		13.0	145.7	8.2	54	0.3	2.7	2.7	93	2.18	16.2	0.7	76.3	2.2	4	0.2	0.7	0.6	73	<0.01	0.036
L90W	110 00 N	Soil		5.6	841.4	99.6	227	0.3	17.6	11.9	1136	5.26	36.7	3.7	12.9	0.5	148	0.9	5.1	0.7	80	0.49	0.097
L90W	110 50 N	Soil		3.1	65.9	112.9	155	0.5	11.4	9.5	940	4.51	36.0	0.9	10.6	0.7	52	0.4	2.8	0.5	87	0.11	0.059
L90W	111 00 N	Soil		6.6	390.3	76.7	376	1.1	15.6	10.6	1063	4.46	151.5	4.7	32.2	1.0	82	0.7	10.2	1.2	64	0.38	0.112
L90W	111 50 N	Soil		3.1	42.1	72.2	73	0.3	10.3	5.6	377	6.72	34.2	1.1	9.3	1.7	17	0.4	2.1	0.6	78	0.09	0.492
L90W	112 00 N	Soil		8.4	122.6	29.3	38	0.2	4.7	3.0	188	3.35	15.6	1.0	25.2	2.0	41	<0.1	0.8	0.5	54	0.18	0.055
L90W	112 50 N	Soil		2.9	46.2	51.8	71	0.7	7.8	4.8	307	5.40	23.9	1.1	11.4	2.5	7	0.1	1.6	0.5	76	0.03	0.244
L90W	113 00 N	Soil		3.5	98.1	20.2	42	0.7	2.7	3.2	122	4.78	16.7	1.2	24.1	3.0	3	<0.1	3.0	0.5	41	<0.01	0.102
L90W	113 50 N	Soil		7.2	348.2	46.5	229	0.4	13.3	14.7	2261	4.09	73.1	2.8	41.4	1.8	52	1.1	7.0	1.3	45	0.27	0.096
L90W	114 00 N	Soil		2.3	37.8	44.3	114	0.6	9.7	5.0	330	3.97	22.9	1.4	8.8	1.4	10	0.4	1.3	0.7	72	0.03	0.080
L90W	114 50 N	Soil		1.4	13.2	19.9	35	0.4	3.2	1.8	135	2.54	17.5	0.5	5.2	0.4	8	0.1	1.2	0.6	89	0.02	0.026
L90W	115 00 N	Soil		2.3	56.7	33.2	89	1.5	10.1	6.8	559	2.96	15.0	3.0	9.8	0.2	24	0.2	1.3	0.8	54	0.09	0.166
L90W	115 50 N	Soil		2.8	97.3	76.5	157	0.6	14.8	9.3	855	5.43	48.2	2.3	27.1	0.6	20	0.3	2.8	2.3	75	0.06	0.076
L90W	116 00 N	Soil		2.6	104.1	103.5	176	5.5	9.0	4.7	348	4.67	37.2	5.1	52.0	0.7	18	0.4	1.8	2.0	52	0.07	0.184

This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.



AcmeLabs ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
Report Date: August 28, 2008

Page: 3 of 8 **Part** 2

CERTIFICATE OF ANALYSIS

SMI08000686.1

Method	Analyte	Unit	MDL	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
				La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
				ppm	ppm	%	ppm	%	ppm	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
				1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.01	0.1	0.01	0.05	1	0.5	
L88W	121 00 N	Soil		7	18	0.32	92	0.020	3	1.58	0.006	0.07	0.1	0.10	2.1	0.2	0.09	8	0.7
L88W	121 50 N	Soil		21	23	0.41	195	0.007	3	2.72	0.007	0.09	0.1	0.16	3.1	0.2	0.08	7	1.8
L88W	122 50 N	Soil		6	19	0.34	98	0.014	2	2.37	0.006	0.05	0.1	0.12	2.6	0.2	<0.05	9	0.7
L88W	123 00 N	Soil		5	21	0.31	86	0.015	3	2.74	0.006	0.05	0.2	0.14	2.5	0.2	<0.05	6	0.6
L88W	123 50 N	Soil		4	16	0.28	91	0.013	2	2.05	0.007	0.05	0.1	0.10	2.0	0.1	<0.05	6	<0.5
L88W	124 00 N	Soil		9	24	0.44	227	0.008	2	2.68	0.007	0.09	0.1	0.09	3.2	0.3	<0.05	7	0.7
L88W	124 50 N	Soil		6	22	0.41	116	0.009	3	2.51	0.006	0.06	<0.1	0.09	3.0	0.2	<0.05	6	<0.5
L90W	105 00 N	Soil		10	17	0.21	175	0.014	3	1.28	0.005	0.07	0.2	0.08	1.4	0.2	<0.05	9	1.1
L90W	105 50 N	Soil		18	12	0.21	96	0.004	1	1.44	0.008	0.06	<0.1	0.13	0.8	0.3	<0.05	5	1.0
L90W	106 00 N	Soil		5	16	0.14	58	0.007	2	1.61	0.004	0.05	0.2	0.10	1.9	0.3	<0.05	8	1.2
L90W	106 50 N	Soil		4	20	0.18	47	0.012	3	2.02	0.004	0.03	0.1	0.10	2.3	0.2	<0.05	6	0.6
L90W	107 00 N	Soil		4	22	0.23	48	0.015	2	1.77	0.004	0.04	0.2	0.09	2.5	0.2	<0.05	8	0.6
L90W	107 50 N	Soil		4	20	0.19	42	0.011	1	1.84	0.004	0.04	0.2	0.16	2.2	0.3	<0.05	9	0.8
L90W	108 00 N	Soil		5	19	0.16	54	0.028	2	1.59	0.004	0.04	0.2	0.09	2.1	0.1	0.06	11	<0.5
L90W	108 50 N	Soil		5	5	0.04	33	0.004	2	0.52	0.004	0.05	0.2	0.04	0.8	0.2	<0.05	5	<0.5
L90W	109 00 N	Soil		7	13	0.08	38	0.006	1	1.25	0.003	0.03	0.1	0.07	1.5	0.1	<0.05	7	<0.5
L90W	109 50 N	Soil		6	5	0.04	26	0.006	<1	0.80	0.003	0.05	0.2	0.05	1.1	0.2	<0.05	7	<0.5
L90W	110 00 N	Soil		13	20	0.31	184	0.020	2	1.53	0.012	0.06	0.2	0.09	3.1	0.1	<0.05	6	2.1
L90W	110 50 N	Soil		7	18	0.24	93	0.013	3	1.29	0.005	0.06	0.2	0.09	2.4	0.2	<0.05	7	0.8
L90W	111 00 N	Soil		15	16	0.30	177	0.012	2	1.50	0.011	0.09	0.2	0.17	5.0	0.2	<0.05	4	1.1
L90W	111 50 N	Soil		5	21	0.21	69	0.015	2	2.58	0.006	0.04	0.2	0.20	2.8	0.2	<0.05	7	1.2
L90W	112 00 N	Soil		8	6	0.18	67	0.003	<1	1.06	0.004	0.09	0.2	0.03	1.5	0.3	<0.05	4	0.6
L90W	112 50 N	Soil		5	18	0.19	50	0.009	<1	3.07	0.006	0.04	0.2	0.13	3.0	0.2	<0.05	7	1.2
L90W	113 00 N	Soil		6	5	0.03	36	0.001	2	1.67	0.002	0.03	0.9	0.05	1.7	0.3	<0.05	5	<0.5
L90W	113 50 N	Soil		13	9	0.21	299	0.009	1	0.97	0.009	0.08	0.3	0.09	3.6	0.2	0.06	3	1.2
L90W	114 00 N	Soil		7	14	0.26	84	0.009	2	2.05	0.004	0.06	0.2	0.16	2.3	0.2	<0.05	7	<0.5
L90W	114 50 N	Soil		5	7	0.04	56	0.015	3	0.74	0.002	0.04	0.2	0.08	0.9	0.2	<0.05	10	<0.5
L90W	115 00 N	Soil		14	13	0.20	87	0.010	2	2.12	0.008	0.06	0.2	0.22	1.6	0.3	0.07	5	0.8
L90W	115 50 N	Soil		11	16	0.25	80	0.009	1	1.78	0.004	0.07	0.2	0.13	2.4	0.2	<0.05	6	1.6
L90W	116 00 N	Soil		15	16	0.18	68	0.005	<1	2.13	0.004	0.06	0.2	0.89	1.4	0.3	<0.05	6	1.2

This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.



AcmeLabs ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
Report Date: August 28, 2008

Page: 4 of 8 **Part** 1

CERTIFICATE OF ANALYSIS

SMI08000686.1

Method	Analyte	Unit	MDL	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15		
				Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	P
				ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	%		
				0.1	0.1	0.1	1	0.1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	2	0.01	0.001
L90W	116 50 N	Soil		2.4	104.7	168.8	311	3.4	9.1	6.3	445	5.84	65.7	3.5	65.3	1.1	19	0.5	2.5	3.2	67	0.09	0.091
L90W	117 00 N	Soil		1.4	45.1	68.2	129	0.2	7.8	5.6	383	3.89	33.6	1.6	22.6	0.3	41	0.4	2.0	1.2	100	0.12	0.059
L90W	117 50 N	Soil		4.8	85.6	59.9	134	0.5	9.0	6.7	562	3.22	43.5	2.1	7.0	0.4	180	0.7	1.6	0.9	81	0.40	0.063
L90W	118 00 N	Soil		7.4	128.7	33.4	62	0.4	9.7	7.1	359	4.28	19.5	1.3	18.9	2.4	20	0.1	1.2	1.4	88	0.03	0.090
L90W	118 50 N	Soil		3.4	403.4	122.7	210	0.8	14.7	14.0	1093	4.57	47.4	2.1	32.4	2.1	15	0.7	1.9	1.2	66	0.05	0.099
L90W	119 00 N	Soil		2.3	212.7	131.9	212	2.2	12.1	10.7	1427	4.43	43.3	2.5	23.9	0.4	52	0.4	2.0	1.4	77	0.17	0.129
L90W	119 50 N	Soil		I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.
L90W	120 00 N	Soil		2.0	77.3	21.8	37	1.3	2.2	2.4	106	1.96	21.3	0.7	71.8	0.3	12	0.1	0.7	0.7	59	0.04	0.024
L130W	92 00 N	Soil		2.1	51.0	92.5	139	0.8	12.5	7.8	699	8.24	119.5	1.4	15.3	2.1	7	0.4	3.4	1.6	87	0.04	0.287
L130W	92 50 N	Soil		2.3	44.7	69.5	150	1.3	9.9	10.6	515	5.19	84.8	1.2	27.3	1.8	10	0.3	3.0	1.8	52	0.06	0.119
L130W	93 00 N	Soil		2.7	74.5	40.8	112	0.3	13.2	8.1	442	6.77	88.7	0.7	8.1	1.4	17	0.6	4.4	0.7	88	0.05	0.047
L130W	93 50 N	Soil		2.1	21.7	21.9	73	0.1	5.7	4.0	304	3.14	51.8	0.5	8.9	0.1	10	0.2	2.5	0.7	76	0.09	0.094
L130W	94 00 N	Soil		3.1	53.9	69.4	97	0.4	10.1	8.0	1006	5.78	110.9	0.7	10.4	0.2	10	0.4	3.5	1.0	90	0.03	0.200
L130W	94 50 N	Soil		2.4	60.9	91.9	188	0.3	10.7	9.3	2072	7.04	92.7	0.8	10.4	0.8	7	0.3	3.7	2.3	70	0.02	0.239
L130W	95 00 N	Soil		3.3	49.5	100.1	153	0.6	8.5	8.1	732	8.14	68.0	0.7	14.6	1.5	5	0.4	3.8	2.2	86	0.01	0.077
L130W	95 50 N	Soil		2.0	54.9	124.0	212	1.4	9.1	12.0	1058	6.45	79.4	1.4	41.8	1.0	19	0.9	2.5	2.2	69	0.30	0.137
L130W	96 00 N	Soil		3.4	89.8	74.5	159	0.8	8.3	6.2	267	5.33	72.0	1.0	19.1	1.8	8	0.6	2.7	1.2	73	0.07	0.069
L130W	96 50 N	Soil		1.4	27.8	46.6	97	0.7	12.9	7.4	337	3.01	41.3	1.3	5.4	0.4	22	0.3	1.5	0.4	64	0.14	0.073
L130W	97 00 N	Soil		2.0	61.9	73.7	108	0.6	5.5	3.1	168	5.05	57.5	3.2	14.4	0.2	17	0.4	1.2	1.1	58	0.11	0.138
L130W	97 50 N	Soil		1.3	19.3	39.1	148	0.1	5.3	3.8	1159	3.70	31.9	0.8	4.3	0.3	41	0.4	1.1	0.8	71	0.30	0.047
L130W	98 50 N	Soil		2.7	53.5	137.7	269	0.7	7.3	19.7	7797	7.04	68.0	4.7	23.8	1.2	23	1.4	5.5	1.3	47	0.19	0.245
L130W	99 00 N	Soil		2.7	32.1	67.8	172	1.5	3.1	7.4	308	6.29	38.1	3.3	4.4	6.5	12	0.8	2.6	0.5	46	0.03	0.116
L130W	99 50 N	Soil		5.1	41.9	58.4	165	0.6	7.7	7.2	328	4.27	28.9	2.0	9.6	2.4	9	0.3	1.5	0.6	70	0.02	0.065
L130W	100 00 N	Soil		3.4	39.2	90.4	134	0.2	7.9	8.5	735	5.33	36.8	1.8	9.4	2.1	11	0.4	2.1	0.8	94	0.05	0.082
L130W	100 50 N	Soil		1.5	34.3	39.2	168	0.8	16.4	11.8	1381	3.82	23.1	3.2	6.3	0.4	44	0.4	1.8	0.4	63	0.27	0.142
L130W	101 00 N	Soil		2.2	54.9	65.0	123	0.6	6.1	13.7	471	6.89	26.8	2.6	39.3	7.3	12	0.6	1.6	1.9	53	0.03	0.514
L130W	101 50 N	Soil		1.9	44.9	70.6	116	0.4	15.2	7.5	324	5.20	45.6	1.2	9.5	1.5	9	0.3	2.3	0.9	72	0.02	0.080
L130W	102 00 N	Soil		67.1	385.5	22.2	43	0.7	2.9	2.6	189	13.52	44.0	0.6	70.1	2.3	7	0.2	2.4	1.2	78	<0.01	0.098
L130W	103 00 N	Soil		3.0	52.5	93.6	140	0.5	17.0	9.6	667	6.24	38.5	1.5	10.1	1.5	11	0.4	2.9	0.7	88	0.02	0.060
L130W	103 50 N	Soil		4.5	26.4	97.1	65	1.3	5.4	11.8	378	3.41	35.7	1.1	6.3	0.8	9	0.3	2.5	1.5	87	0.03	0.069

This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.



AcmeLabs ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
Report Date: August 28, 2008

Page: 4 of 8 **Part** 2

CERTIFICATE OF ANALYSIS

SMI08000686.1

Method	Analyte	Unit	MDL	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
				La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
				ppm	ppm	%	ppm	%	ppm	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
				1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.01	0.1	0.01	0.05	1	0.5	
L90W	116 50 N	Soil		20	16	0.21	94	0.008	1	2.18	0.005	0.04	0.2	0.54	3.2	0.3	<0.05	7	1.6
L90W	117 00 N	Soil		10	13	0.11	171	0.016	<1	1.09	0.004	0.06	0.2	0.07	2.3	0.1	<0.05	7	<0.5
L90W	117 50 N	Soil		15	11	0.09	181	0.012	<1	0.79	0.009	0.06	0.2	0.06	1.9	0.1	0.05	5	0.5
L90W	118 00 N	Soil		5	14	0.26	70	0.015	2	1.43	0.006	0.05	0.2	0.11	2.8	0.1	<0.05	6	1.9
L90W	118 50 N	Soil		8	18	0.29	96	0.010	2	2.81	0.006	0.05	0.2	0.18	3.1	0.2	<0.05	5	1.7
L90W	119 00 N	Soil		12	18	0.31	215	0.012	3	1.92	0.007	0.09	0.2	0.15	2.5	0.3	<0.05	6	2.1
L90W	119 50 N	Soil		I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.
L90W	120 00 N	Soil		9	7	0.03	62	0.008	1	0.58	0.003	0.05	<0.1	0.09	0.6	0.2	<0.05	4	<0.5
L130W	92 00 N	Soil		7	27	0.23	58	0.018	2	2.85	0.005	0.04	0.3	0.27	3.7	0.2	<0.05	11	1.2
L130W	92 50 N	Soil		10	18	0.17	45	0.011	1	3.82	0.005	0.03	0.2	0.37	3.6	0.2	<0.05	5	1.6
L130W	93 00 N	Soil		5	26	0.24	98	0.016	2	2.13	0.005	0.04	0.1	0.12	3.4	0.2	<0.05	8	<0.5
L130W	93 50 N	Soil		5	10	0.08	43	0.007	<1	1.02	0.002	0.04	0.3	0.04	1.2	0.1	0.05	7	<0.5
L130W	94 00 N	Soil		6	17	0.13	63	0.010	1	1.59	0.005	0.06	0.1	0.08	1.4	0.3	<0.05	11	<0.5
L130W	94 50 N	Soil		8	17	0.18	50	0.010	<1	1.72	0.004	0.04	0.2	0.11	2.5	0.3	<0.05	8	0.8
L130W	95 00 N	Soil		8	15	0.09	50	0.009	<1	1.59	0.003	0.03	0.2	0.08	3.1	0.3	<0.05	10	<0.5
L130W	95 50 N	Soil		17	17	0.16	75	0.009	<1	2.09	0.005	0.04	0.2	0.14	3.8	0.2	<0.05	9	0.9
L130W	96 00 N	Soil		8	16	0.16	59	0.007	<1	2.29	0.004	0.03	0.2	0.12	3.4	0.2	<0.05	7	0.9
L130W	96 50 N	Soil		9	19	0.29	108	0.006	2	1.89	0.006	0.05	0.1	0.11	1.9	0.3	<0.05	7	<0.5
L130W	97 00 N	Soil		13	13	0.10	70	0.007	1	1.68	0.005	0.05	0.2	0.21	1.2	0.2	0.06	7	1.0
L130W	97 50 N	Soil		7	11	0.09	197	0.014	1	0.80	0.004	0.04	0.1	0.03	1.6	0.1	<0.05	8	0.6
L130W	98 50 N	Soil		20	10	0.14	183	0.008	<1	1.93	0.004	0.04	0.2	0.12	2.2	0.3	0.07	4	1.8
L130W	99 00 N	Soil		32	5	0.05	143	0.002	2	1.85	0.005	0.05	0.2	0.11	2.4	0.3	<0.05	6	1.0
L130W	99 50 N	Soil		14	12	0.20	88	0.003	<1	2.01	0.005	0.04	0.1	0.09	2.7	0.2	<0.05	7	<0.5
L130W	100 00 N	Soil		9	17	0.13	86	0.009	1	2.36	0.003	0.04	0.3	0.12	2.7	0.3	<0.05	9	0.6
L130W	100 50 N	Soil		16	19	0.33	182	0.008	2	1.63	0.009	0.05	0.1	0.08	1.9	0.1	<0.05	5	<0.5
L130W	101 00 N	Soil		16	8	0.09	78	0.005	2	2.89	0.005	0.04	0.2	0.34	4.0	0.3	<0.05	4	0.9
L130W	101 50 N	Soil		7	23	0.33	59	0.005	1	2.26	0.004	0.05	0.2	0.15	3.1	0.2	<0.05	6	1.1
L130W	102 00 N	Soil		6	10	0.04	28	0.005	1	1.04	0.005	0.04	0.1	0.07	2.3	0.3	0.07	6	3.9
L130W	103 00 N	Soil		9	27	0.33	58	0.009	2	2.49	0.004	0.06	0.1	0.15	4.2	0.2	<0.05	8	1.2
L130W	103 50 N	Soil		10	14	0.14	68	0.008	2	1.58	0.005	0.05	0.2	0.11	1.4	0.3	<0.05	9	0.8

This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.



AcmeLabs ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
Report Date: August 28, 2008

Page: 5 of 8 **Part** 1

CERTIFICATE OF ANALYSIS

SMI08000686.1

Method	Analyte	Unit	MDL	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15		
				Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	P
				ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	%		
				0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	0.001
L130W	104 00 N	Soil		8.1	62.3	54.7	82	1.0	9.8	7.0	331	4.29	35.9	1.1	6.6	0.3	14	0.6	2.1	0.7	82	0.04	0.060
L130W	104 50 N	Soil		8.7	153.0	173.7	167	1.4	14.3	8.2	438	5.19	87.7	4.7	39.2	0.9	16	0.3	2.2	1.6	58	0.10	0.136
L130W	105 00 N	Soil		19.0	323.6	183.1	136	2.3	13.2	128.0	5999	5.32	81.8	5.6	72.3	3.6	23	0.5	2.0	1.3	43	0.07	0.247
L130W	105 50 N	Soil		3.1	63.5	68.6	104	2.0	10.3	6.1	337	5.13	92.0	2.2	21.2	0.9	13	0.4	2.5	1.5	77	0.04	0.129
L130W	106 00 N	Soil		3.1	58.2	60.2	147	0.2	11.1	6.4	352	4.77	87.3	1.1	22.7	0.2	25	0.8	2.1	2.7	77	0.06	0.086
L130W	107 75N	Soil		8.2	336.6	69.9	66	0.6	6.1	9.1	1722	8.69	56.2	3.5	35.2	1.9	36	0.2	3.5	1.5	64	0.14	0.157
L130W	108 60 N	Soil		1.9	36.9	15.3	63	<0.1	7.6	6.9	679	5.43	22.9	0.4	3.9	0.5	7	0.3	0.8	0.5	123	0.03	0.095
L130W	109 00 N	Soil		1.5	11.3	5.9	16	<0.1	2.1	1.3	69	0.80	5.5	0.2	9.4	0.4	7	<0.1	0.4	0.2	37	0.04	0.025
L130W	109 50 N	Soil		1.8	50.9	31.1	95	0.2	12.0	8.8	638	4.29	20.5	0.8	4.9	0.7	9	0.3	1.1	0.6	82	0.04	0.089
L130W	110 00 N	Soil		1.7	32.6	24.0	55	<0.1	9.6	5.6	373	3.52	17.4	0.5	3.7	0.4	11	0.4	1.1	0.5	91	0.11	0.042
L130W	110 50 N	Soil		2.1	51.1	42.8	75	0.3	13.4	8.3	530	7.91	25.0	0.9	7.9	1.7	5	0.3	1.2	0.6	89	0.02	0.070
L130W	111 00 N	Soil		3.0	50.5	48.8	274	0.3	25.3	19.7	2279	4.65	31.2	2.6	5.4	0.8	34	0.6	2.1	0.5	78	0.39	0.192
L130W	111 50 N	Soil		1.6	28.6	32.0	69	<0.1	14.5	6.5	322	6.19	30.2	0.7	11.8	0.9	12	0.3	1.7	0.4	100	0.02	0.052
L130W	112 00 N	Soil		2.1	42.3	27.4	65	0.3	13.5	6.4	361	5.93	22.9	1.3	6.5	0.7	10	0.3	1.4	0.4	80	0.04	0.066
L132W	92 00 N	Soil		2.1	39.8	86.5	109	0.5	14.3	6.6	323	5.33	61.9	1.0	23.8	1.3	11	0.4	2.7	1.2	67	0.05	0.068
L132W	92 50 N	Soil		1.9	64.1	63.5	358	0.5	55.9	14.5	528	4.28	40.2	1.3	10.9	1.0	29	0.5	2.3	0.5	63	0.25	0.105
L132W	93 00 N	Soil		2.0	63.4	97.5	161	0.6	9.7	7.2	697	9.06	104.8	0.8	15.9	0.8	8	0.7	6.1	1.7	72	0.03	0.093
L132W	93 50 N	Soil		I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.
L132W	94 00 N	Soil		2.1	61.4	272.6	240	0.7	7.6	18.8	2414	9.38	192.6	0.5	12.0	1.1	4	0.7	8.7	2.4	34	0.04	0.097
L132W	94 50 N	Soil		2.7	36.9	97.4	189	1.1	8.1	6.7	640	4.53	54.5	0.8	14.9	0.8	13	0.9	2.3	1.6	58	0.14	0.101
L132W	95 00 N	Soil		2.5	54.4	98.2	215	2.0	10.1	6.1	587	4.84	95.4	0.8	19.2	1.0	8	0.5	3.6	1.9	64	0.05	0.081
L132W	95 50 N	Soil		2.6	156.6	106.4	177	1.1	11.4	10.3	984	4.75	70.3	2.0	18.6	0.2	27	1.7	2.9	1.9	70	0.26	0.114
L132W	96 00 N	Soil		1.9	49.8	69.5	193	1.7	11.5	7.1	654	4.44	53.9	0.9	15.3	0.6	18	0.7	2.1	1.3	71	0.14	0.079
L132W	96 50 N	Soil		2.5	101.3	88.4	129	1.2	12.0	6.9	605	4.93	48.4	2.0	14.8	0.9	13	0.4	1.8	0.9	69	0.07	0.077
L132W	97 00 N	Soil		I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.
L132W	97 50 N	Soil		2.1	33.4	90.8	169	1.4	7.9	21.4	1249	6.05	78.2	1.0	7.9	1.2	23	0.8	1.5	0.9	72	0.26	0.064
L132W	98 00 N	Soil		1.6	38.1	36.3	51	0.4	5.6	8.2	246	6.46	28.8	0.5	3.6	0.6	6	0.3	0.8	1.0	118	0.04	0.088
L132W	98 50 N	Soil		1.3	26.9	33.7	165	0.2	7.2	11.4	1762	4.30	28.6	0.7	9.1	<0.1	24	0.7	1.4	0.8	66	0.41	0.157
L132W	99 00 N	Soil		2.3	41.2	46.7	163	0.4	8.9	6.3	408	5.77	50.4	0.5	7.2	0.3	7	0.2	2.0	1.0	80	0.02	0.165
L132W	99 50 N	Soil		2.5	53.3	78.7	154	1.0	8.5	9.5	758	10.64	58.8	1.1	19.1	1.1	6	0.5	2.1	1.4	93	0.02	0.303

This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.



AcmeLabs ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
Report Date: August 28, 2008

Page: 5 of 8 **Part** 2

CERTIFICATE OF ANALYSIS

SMI08000686.1

Method	Analyte	Unit	MDL	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
				La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
				ppm	ppm	%	ppm	%	ppm	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
				1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.01	0.01	0.05	1	0.05	0.5	
L130W	104 00 N	Soil		6	17	0.26	72	0.009	2	1.55	0.005	0.05	0.1	0.11	1.7	0.2	<0.05	7	1.1
L130W	104 50 N	Soil		14	22	0.30	63	0.010	<1	2.48	0.006	0.06	0.2	0.36	3.0	0.2	<0.05	7	1.7
L130W	105 00 N	Soil		25	27	0.26	67	0.026	1	5.31	0.007	0.05	0.2	0.66	5.7	0.5	0.12	8	2.8
L130W	105 50 N	Soil		10	20	0.26	56	0.010	2	2.66	0.004	0.05	0.2	0.38	2.6	0.3	<0.05	7	1.4
L130W	106 00 N	Soil		8	15	0.18	108	0.007	<1	1.35	0.005	0.05	0.1	0.09	1.4	0.2	0.05	7	0.7
L130W	107 75N	Soil		12	15	0.13	55	0.009	2	2.13	0.004	0.05	0.1	0.30	2.3	0.3	0.08	8	4.9
L130W	108 60 N	Soil		6	14	0.25	40	0.005	1	1.89	0.004	0.04	<0.1	0.12	2.7	0.1	<0.05	11	<0.5
L130W	109 00 N	Soil		7	5	0.03	54	0.004	3	0.79	0.004	0.04	0.1	0.03	0.8	0.3	<0.05	6	<0.5
L130W	109 50 N	Soil		6	18	0.20	116	0.006	<1	1.76	0.005	0.07	0.1	0.11	3.2	0.2	<0.05	9	<0.5
L130W	110 00 N	Soil		5	18	0.14	84	0.007	1	1.30	0.005	0.07	<0.1	0.06	1.8	0.2	<0.05	8	<0.5
L130W	110 50 N	Soil		4	27	0.27	48	0.006	1	2.72	0.004	0.05	<0.1	0.25	3.9	0.2	<0.05	9	1.1
L130W	111 00 N	Soil		21	23	0.41	151	0.012	2	2.46	0.009	0.07	<0.1	0.11	5.0	0.1	0.05	7	1.4
L130W	111 50 N	Soil		4	24	0.28	66	0.018	1	2.40	0.004	0.05	<0.1	0.10	2.9	0.2	<0.05	11	0.6
L130W	112 00 N	Soil		6	24	0.29	48	0.021	1	2.96	0.005	0.03	0.2	0.16	3.1	0.1	<0.05	8	1.6
L132W	92 00 N	Soil		7	24	0.29	66	0.011	2	3.02	0.007	0.04	0.2	0.22	2.9	0.2	<0.05	6	1.0
L132W	92 50 N	Soil		12	26	0.36	135	0.015	3	3.22	0.012	0.09	0.2	0.27	4.4	0.2	<0.05	7	1.4
L132W	93 00 N	Soil		7	18	0.12	58	0.012	<1	1.61	0.004	0.04	0.2	0.09	3.1	0.2	<0.05	8	0.8
L132W	93 50 N	Soil		I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.
L132W	94 00 N	Soil		11	10	0.04	54	0.003	1	1.02	0.003	0.04	0.2	0.17	2.7	0.2	<0.05	3	1.7
L132W	94 50 N	Soil		9	15	0.12	89	0.006	<1	1.92	0.005	0.05	0.2	0.18	1.6	0.2	<0.05	7	0.6
L132W	95 00 N	Soil		7	19	0.19	54	0.006	2	1.74	0.005	0.06	0.2	0.21	2.1	0.3	<0.05	6	0.8
L132W	95 50 N	Soil		16	16	0.13	137	0.009	1	1.57	0.007	0.08	0.2	0.12	1.5	0.3	0.06	7	0.9
L132W	96 00 N	Soil		8	17	0.26	95	0.007	2	1.68	0.006	0.06	0.1	0.11	2.0	0.2	<0.05	6	0.8
L132W	96 50 N	Soil		10	21	0.19	78	0.009	2	2.34	0.007	0.05	0.2	0.15	2.4	0.2	<0.05	9	1.0
L132W	97 00 N	Soil		I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.
L132W	97 50 N	Soil		9	13	0.17	99	0.004	1	1.61	0.005	0.05	0.1	0.11	2.4	0.2	<0.05	5	0.9
L132W	98 00 N	Soil		5	17	0.26	61	0.002	<1	1.33	0.006	0.03	<0.1	0.04	4.8	0.1	<0.05	8	0.6
L132W	98 50 N	Soil		5	11	0.10	135	0.006	2	0.80	0.004	0.08	0.1	0.10	0.7	0.2	0.08	6	<0.5
L132W	99 00 N	Soil		7	15	0.18	70	0.009	2	1.44	0.004	0.04	0.2	0.12	1.8	0.3	<0.05	8	0.5
L132W	99 50 N	Soil		12	13	0.20	53	0.015	1	1.87	0.005	0.03	0.2	0.12	2.5	0.2	<0.05	11	0.9

This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.



AcmeLabs ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
Report Date: August 28, 2008

Page: 6 of 8 **Part** 1

CERTIFICATE OF ANALYSIS

SMI08000686.1

Method	Analyte	Unit	MDL	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15		
				Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	P
				ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	%		
				0.1	0.1	0.1	1	0.1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	2	0.01	0.001
L132W 100 00 N	Soil			2.4	52.7	65.3	126	0.8	11.3	6.0	477	5.94	45.0	1.2	39.7	1.5	10	0.3	2.5	0.9	70	0.04	0.119
L132W 100 50 N	Soil			1.7	46.8	58.0	192	1.6	12.0	6.7	294	3.44	28.8	1.4	8.3	0.3	14	0.6	2.0	0.7	71	0.05	0.065
L132W 101 00 N	Soil			2.2	75.3	106.7	153	0.5	13.1	9.2	1030	4.14	56.7	1.3	29.5	1.6	11	0.4	2.2	1.3	60	0.05	0.104
L132W 101 50 N	Soil			1.4	23.1	104.8	70	1.0	6.7	4.9	1792	3.88	38.6	0.6	10.7	0.2	10	0.3	1.3	1.5	74	0.02	0.131
L132W 102 00 N	Soil			2.2	58.6	78.3	241	0.6	13.1	11.4	713	4.77	56.5	1.2	10.8	0.4	18	0.8	1.8	1.1	65	0.12	0.083
L132W 102 50 N	Soil			2.8	163.0	114.4	99	1.0	6.4	10.2	959	14.43	149.6	3.4	202.6	0.6	6	0.9	3.2	17.4	43	0.03	0.321
L132W 103 00 N	Soil			I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.
L132W 103 50 N	Soil			4.2	62.1	69.3	92	0.4	13.3	6.4	388	6.47	52.1	0.7	9.0	1.5	8	0.3	2.1	0.6	81	0.02	0.064
L132W 104 00 N	Soil			4.5	49.0	74.4	93	0.7	11.2	6.2	395	6.28	58.6	0.9	13.6	1.5	8	0.2	2.3	1.0	83	0.02	0.111
L132W 104 50 N	Soil			54.9	193.6	53.9	46	0.4	5.2	7.3	366	6.45	106.8	0.9	23.8	0.9	6	0.2	1.8	0.9	80	0.01	0.130
L132W 105 00 N	Soil			33.2	234.8	61.0	61	0.7	6.9	9.1	708	10.19	49.8	0.6	64.3	1.5	4	0.1	1.2	1.3	45	<0.01	0.182
L132W 105 50 N	Soil			11.4	303.0	85.4	143	1.4	17.4	41.7	1246	8.30	86.5	1.8	25.7	0.5	16	0.4	2.7	1.0	72	0.05	0.075
L132W 106 00 N	Soil			3.7	235.7	72.9	193	1.4	21.7	8.0	296	3.46	44.5	2.1	17.3	0.6	25	0.2	2.0	0.6	52	0.14	0.100
L132W 106 50 N	Soil			I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.
L132W 107 00 N	Soil			3.2	30.8	32.7	52	0.2	3.6	18.2	4623	5.50	44.1	0.8	11.5	0.3	11	0.1	1.0	1.2	63	0.02	0.075
L132W 107 50 N	Soil			5.2	73.1	40.5	68	1.1	7.2	4.4	193	5.05	39.6	1.3	13.8	0.5	32	0.2	1.6	1.0	81	0.11	0.099
L132W 108 00 N	Soil			19.2	85.5	41.5	60	0.3	9.7	6.4	370	6.05	34.5	1.4	21.7	1.0	9	0.9	1.8	1.6	68	0.05	0.123
L132W 108 50 N	Soil			7.8	64.1	33.8	36	1.1	4.7	20.3	1568	4.53	37.1	1.3	12.3	0.3	26	0.2	1.3	0.4	55	0.08	0.202
L132W 109 00 N	Soil			2.6	36.2	23.7	21	1.0	2.6	17.2	5747	2.60	9.4	0.7	16.4	0.4	26	0.3	0.5	0.5	28	0.07	0.077
L132W 109 50 N	Soil			1.5	23.0	19.0	48	0.6	9.3	3.5	139	3.17	14.9	0.9	4.9	0.3	23	0.3	0.5	0.4	66	0.16	0.093
L132W 110 00 N	Soil			0.4	48.9	32.7	15	1.6	5.2	2.6	122	0.54	2.5	2.9	7.8	0.5	33	0.3	1.2	0.1	10	0.42	0.380
L132W 110 50 N	Soil			1.6	49.9	34.2	91	0.2	18.1	8.7	386	4.81	29.4	1.0	3.5	0.4	27	0.5	1.3	0.5	82	0.25	0.072
L132W 111 00 N	Soil			1.5	37.5	30.6	77	0.2	14.2	7.6	369	5.99	23.7	0.8	6.5	1.5	9	0.1	1.2	0.3	92	0.02	0.047
L132W 111 50 N	Soil			3.0	41.2	28.5	66	0.4	9.2	5.2	378	4.55	26.2	1.1	11.8	0.2	9	0.3	1.5	0.7	85	0.02	0.119
L132W 112 00 N	Soil			1.9	29.9	28.8	46	0.3	9.9	4.6	386	5.48	24.2	0.8	8.3	0.5	7	0.2	1.1	0.5	97	0.02	0.130
L134W 92 00 N	Soil			1.1	17.7	20.3	44	0.2	5.4	2.6	158	3.06	25.6	0.4	2.8	0.5	11	0.2	2.0	0.5	82	0.04	0.022
L134W 92 50 N	Soil			1.6	122.9	98.0	376	1.8	25.9	14.7	2347	4.68	58.5	2.0	20.1	0.5	21	1.3	2.4	0.9	51	0.23	0.169
L134W 93 00 N	Soil			2.2	46.9	57.2	114	0.7	9.2	9.6	6203	3.87	74.6	1.0	13.2	0.1	20	2.2	2.4	1.7	62	0.22	0.092
L134W 93 50 N	Soil			2.2	37.5	46.9	115	0.2	8.3	5.9	469	3.87	61.0	0.9	3.9	0.7	13	0.4	2.8	0.7	82	0.08	0.044
L134W 94 00 N	Soil			2.1	36.2	70.6	124	0.5	8.6	5.9	650	7.03	106.0	0.7	11.1	1.2	8	0.3	3.0	1.7	81	0.03	0.202

This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
 Report Date: August 28, 2008

Page: 6 of 8 Part 2

CERTIFICATE OF ANALYSIS

SMI08000686.1

Method	Analyte	Unit	MDL	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
				La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
				ppm	ppm	%	ppm	%	ppm	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
				1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.05	1	0.05	
L132W 100 00 N	Soil			7	20	0.25	50	0.009	2	2.34	0.004	0.04	0.2	0.18	2.5	0.2	0.06	7	0.9
L132W 100 50 N	Soil			9	20	0.21	95	0.010	2	2.15	0.005	0.06	0.1	0.17	2.2	0.3	<0.05	8	1.0
L132W 101 00 N	Soil			9	20	0.27	58	0.007	2	2.31	0.005	0.05	0.1	0.20	2.8	0.2	<0.05	5	0.9
L132W 101 50 N	Soil			7	13	0.13	73	0.012	2	1.32	0.004	0.05	0.1	0.11	1.2	0.4	<0.05	8	<0.5
L132W 102 00 N	Soil			10	16	0.24	114	0.007	1	1.66	0.006	0.06	0.2	0.06	1.9	0.2	<0.05	6	0.6
L132W 102 50 N	Soil			17	7	0.04	61	0.014	3	1.27	0.004	0.05	0.2	0.24	1.5	0.3	0.09	4	3.3
L132W 103 00 N	Soil			I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.
L132W 103 50 N	Soil			5	22	0.24	63	0.013	2	2.37	0.007	0.04	0.2	0.16	3.2	0.2	<0.05	8	0.9
L132W 104 00 N	Soil			6	19	0.23	61	0.011	2	2.18	0.005	0.06	0.2	0.14	2.7	0.2	<0.05	9	0.8
L132W 104 50 N	Soil			5	8	0.18	43	0.006	2	1.70	0.004	0.07	0.1	0.10	2.0	0.5	<0.05	8	2.7
L132W 105 00 N	Soil			4	11	0.21	31	0.005	<1	1.68	0.005	0.06	<0.1	0.13	2.6	0.3	0.07	5	7.4
L132W 105 50 N	Soil			35	17	0.25	44	0.015	2	2.09	0.006	0.05	0.2	0.11	2.7	0.2	0.08	8	4.3
L132W 106 00 N	Soil			17	16	0.30	71	0.008	2	1.91	0.008	0.06	0.1	0.30	2.7	0.2	0.05	4	1.6
L132W 106 50 N	Soil			I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.
L132W 107 00 N	Soil			7	12	0.07	83	0.009	<1	1.35	0.005	0.04	0.1	0.05	1.6	0.3	<0.05	8	0.8
L132W 107 50 N	Soil			10	14	0.16	63	0.006	1	1.80	0.005	0.06	0.2	0.13	2.0	0.2	<0.05	9	0.9
L132W 108 00 N	Soil			8	16	0.20	74	0.005	1	2.05	0.004	0.05	0.1	0.17	2.3	0.2	0.05	7	1.8
L132W 108 50 N	Soil			9	11	0.10	98	0.005	1	1.64	0.005	0.05	0.1	0.27	1.5	0.4	0.09	6	2.2
L132W 109 00 N	Soil			6	8	0.05	112	0.004	<1	1.20	0.005	0.05	<0.1	0.13	1.1	0.3	<0.05	6	0.6
L132W 109 50 N	Soil			7	17	0.21	120	0.008	2	2.29	0.007	0.05	0.1	0.14	2.0	0.1	0.06	10	<0.5
L132W 110 00 N	Soil			37	9	0.09	131	0.009	2	2.81	0.008	0.03	<0.1	0.37	5.3	0.2	0.25	2	2.2
L132W 110 50 N	Soil			7	22	0.32	156	0.013	3	2.22	0.008	0.10	0.1	0.11	3.2	0.2	<0.05	9	0.7
L132W 111 00 N	Soil			4	26	0.32	55	0.012	2	3.10	0.005	0.07	0.1	0.18	4.4	0.2	<0.05	10	0.9
L132W 111 50 N	Soil			7	18	0.20	54	0.014	2	2.25	0.007	0.06	0.1	0.12	1.6	0.2	<0.05	10	1.2
L132W 112 00 N	Soil			5	20	0.21	46	0.012	1	1.95	0.004	0.06	0.1	0.13	2.4	0.2	<0.05	9	0.8
L134W 92 00 N	Soil			5	13	0.07	52	0.022	2	1.00	0.003	0.04	0.1	0.06	1.8	0.2	<0.05	7	<0.5
L134W 92 50 N	Soil			16	23	0.37	115	0.014	3	2.40	0.009	0.07	0.1	0.32	3.1	0.2	0.08	7	1.2
L134W 93 00 N	Soil			11	14	0.11	133	0.008	2	1.35	0.005	0.07	0.1	0.12	1.7	0.4	0.05	8	0.8
L134W 93 50 N	Soil			12	13	0.11	92	0.012	2	1.12	0.003	0.06	0.1	0.04	2.3	0.3	0.07	8	<0.5
L134W 94 00 N	Soil			9	17	0.14	73	0.014	2	1.83	0.004	0.06	0.2	0.10	3.0	0.3	<0.05	11	<0.5

This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.



AcmeLabs ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
Report Date: August 28, 2008

Page: 7 of 8 **Part** 1

CERTIFICATE OF ANALYSIS

SMI08000686.1

Method	Analyte	Unit	MDL	1DX15 Mo	1DX15 Cu	1DX15 Pb	1DX15 Zn	1DX15 Ag	1DX15 Ni	1DX15 Co	1DX15 Mn	1DX15 Fe	1DX15 As	1DX15 U	1DX15 Au	1DX15 Th	1DX15 Sr	1DX15 Cd	1DX15 Sb	1DX15 Bi	1DX15 V	1DX15 Ca	1DX15 P
				ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	%
				0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	0.001
L134W 94 50 N	Soil			1.7	31.7	41.7	71	0.3	7.3	4.8	423	3.92	99.1	0.5	8.6	0.3	8	0.3	2.4	2.0	64	0.03	0.197
L134W 95 00 N	Soil			1.6	47.3	161.6	135	1.4	12.1	8.4	858	4.58	44.5	0.8	28.3	0.6	7	0.8	2.1	1.1	59	0.04	0.070
L134W 95 50 N	Soil			2.4	58.2	51.1	135	0.2	8.3	6.1	394	3.92	57.9	0.6	19.4	0.4	12	0.4	3.9	1.5	71	0.12	0.060
L134W 96 00 N	Soil			1.5	51.2	77.8	207	2.2	12.0	5.4	260	4.07	44.6	1.8	8.5	0.4	13	0.6	1.9	0.5	49	0.09	0.080
L134W 96 50 N	Soil			4.8	46.3	76.9	74	0.6	5.3	3.8	250	5.35	51.3	0.7	19.4	0.6	6	0.3	2.6	1.7	96	0.01	0.134
L134W 97 00 N	Soil			1.2	10.7	19.8	27	0.9	5.2	2.6	131	2.43	9.4	0.6	0.5	<0.1	7	0.3	0.3	0.3	48	0.04	0.045
L134W 97 50 N	Soil			2.0	39.1	59.4	90	0.4	7.2	3.8	216	3.79	37.9	0.8	7.6	1.4	7	0.3	1.2	0.8	47	0.02	0.050
L134W 98 00 N	Soil			1.2	29.1	57.2	75	0.5	6.5	4.7	335	4.87	107.7	0.8	20.1	0.4	8	0.3	1.8	0.7	85	0.04	0.067
L134W 98 50 N	Soil			2.6	49.4	50.9	128	0.6	12.4	5.4	223	4.53	26.3	1.2	9.8	0.7	10	0.2	1.3	0.5	60	0.05	0.056
L134W 99 00 N	Soil			2.2	36.1	74.9	72	0.5	8.3	4.3	297	3.91	38.3	1.2	12.7	0.4	7	0.2	1.7	0.9	69	0.03	0.069
L134W 99 50 N	Soil			5.8	133.3	66.5	324	2.7	59.2	22.4	5579	5.28	46.7	4.0	9.6	0.8	49	4.8	2.3	0.8	68	0.50	0.184
L134W 100 00 N	Soil			I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.
L134W 100 50 N	Soil			18.0	42.3	50.5	49	1.5	6.0	3.6	191	7.43	26.1	0.8	31.1	1.6	6	<0.1	2.1	0.8	97	0.02	0.141
L134W 101 00 N	Soil			7.0	78.8	86.4	119	0.7	10.8	9.1	515	11.32	113.4	1.0	48.4	2.2	5	0.4	3.3	2.6	109	0.02	0.234
L134W 101 50 N	Soil			3.6	52.1	56.9	103	0.8	12.1	6.8	307	5.41	56.7	1.6	13.5	1.1	6	0.2	2.1	1.1	74	0.02	0.079
L134W 102 00 N	Soil			3.8	92.9	111.2	129	1.8	11.1	9.8	534	6.31	78.8	5.3	37.2	0.8	7	0.4	2.4	2.4	71	0.03	0.118
L134W 102 50 N	Soil			4.1	51.7	107.4	57	1.2	7.1	4.8	142	4.08	57.4	1.2	34.2	1.1	15	<0.1	4.3	1.7	85	0.10	0.122
L134W 103 00 N	Soil			4.3	153.1	138.0	92	0.6	11.9	21.6	953	8.30	48.5	6.3	8.5	1.3	12	0.1	3.6	1.0	73	0.04	0.132
L134W 103 50 N	Soil			4.7	16.4	25.8	44	0.2	5.0	2.8	163	2.95	17.8	0.5	2.4	0.2	9	<0.1	1.4	0.5	76	0.02	0.054
L134W 104 00 N	Soil			5.1	28.1	32.6	47	0.5	6.7	4.9	305	4.43	32.5	0.7	3.7	0.2	8	0.2	2.1	0.6	77	0.01	0.079
L134W 104 50 N	Soil			14.1	54.7	80.0	75	0.3	9.2	6.9	897	7.27	39.6	1.1	6.2	1.6	7	0.2	2.5	0.9	100	0.01	0.096
L134W 105 00 N	Soil			17.2	546.6	29.7	16	1.7	3.6	46.2	891	2.48	31.2	48.1	18.1	9.2	2	0.2	1.0	0.2	19	0.03	0.262
L134W 105 50 N	Soil			20.4	354.1	77.5	103	0.3	11.0	11.9	581	7.94	85.1	2.2	76.1	2.0	7	<0.1	3.0	1.2	65	0.05	0.162
L134W 106 00 N	Soil			6.2	1080	62.0	121	0.2	13.1	14.9	590	3.72	66.6	1.7	16.6	0.3	60	0.3	1.8	1.3	60	0.28	0.103
L134W 106 50 N	Soil			29.1	450.7	61.9	73	0.9	7.4	10.5	310	6.98	45.1	1.2	72.5	0.8	82	0.6	2.5	1.2	70	0.37	0.109
L134W 107 00 N	Soil			23.2	428.7	54.6	89	0.3	10.4	6.6	367	5.13	43.9	1.1	17.3	0.4	57	0.3	2.3	1.0	83	0.20	0.074
L134W 107 50 N	Soil			36.1	1102	26.8	37	0.9	4.8	9.3	144	6.27	10.5	1.3	151.2	2.3	5	0.2	0.8	0.5	81	0.04	0.121
L134W 108 00 N	Soil			48.3	796.0	27.8	17	0.3	5.0	25.9	246	9.24	12.5	1.8	72.7	5.1	20	0.8	2.2	0.4	33	0.15	0.160
L134W 108 50 N	Soil			30.9	1709	51.4	69	0.7	11.2	33.6	1820	5.05	45.5	2.3	40.6	0.9	188	0.3	1.8	0.6	45	0.66	0.199
L134W 109 00 N	Soil			3.4	55.7	23.1	50	1.0	7.6	3.0	189	3.70	21.4	1.7	6.5	0.2	9	0.2	0.7	0.6	52	0.03	0.097

This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.



AcmeLabs ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
Report Date: August 28, 2008

Page: 7 of 8 **Part** 2

CERTIFICATE OF ANALYSIS

SMI08000686.1

Method	Analyte	Unit	MDL	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15		
				La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
				ppm	ppm	%	ppm	%	ppm	%	ppm	ppm	ppm	ppm	%	ppm	ppm		
				1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.01	0.01	0.05	1	0.5		
L134W 94 50 N	Soil			9	11	0.10	48	0.014	2	1.00	0.004	0.05	0.1	0.06	1.6	0.3	<0.05	9	0.8
L134W 95 00 N	Soil			6	15	0.21	62	0.006	<1	1.52	0.004	0.04	0.2	0.09	1.6	0.2	<0.05	7	<0.5
L134W 95 50 N	Soil			7	12	0.10	125	0.009	1	0.88	0.003	0.05	0.1	0.08	1.7	0.2	<0.05	6	<0.5
L134W 96 00 N	Soil			13	17	0.20	70	0.005	<1	1.89	0.004	0.04	0.2	0.32	1.8	0.2	<0.05	7	1.5
L134W 96 50 N	Soil			8	9	0.09	47	0.007	<1	1.44	0.003	0.03	0.2	0.13	1.3	0.2	<0.05	8	0.7
L134W 97 00 N	Soil			4	11	0.14	46	0.008	<1	1.31	0.005	0.03	0.1	0.08	0.6	<0.1	<0.05	7	<0.5
L134W 97 50 N	Soil			7	10	0.12	48	0.008	<1	1.83	0.004	0.03	0.2	0.11	1.9	0.3	<0.05	6	<0.5
L134W 98 00 N	Soil			6	13	0.10	69	0.011	<1	1.22	0.003	0.05	0.2	0.09	1.4	0.2	<0.05	8	0.7
L134W 98 50 N	Soil			7	18	0.32	40	0.008	<1	1.47	0.004	0.04	0.1	0.16	1.8	<0.1	<0.05	5	1.3
L134W 99 00 N	Soil			7	16	0.20	45	0.009	<1	1.52	0.004	0.05	0.2	0.10	1.4	0.2	<0.05	8	0.9
L134W 99 50 N	Soil			20	18	0.32	236	0.009	<1	1.84	0.009	0.07	0.2	0.14	3.5	0.5	<0.05	6	0.9
L134W 100 00 N	Soil			I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.
L134W 100 50 N	Soil			6	15	0.11	37	0.013	<1	1.37	0.004	0.03	0.2	0.14	1.5	0.2	<0.05	11	0.8
L134W 101 00 N	Soil			7	21	0.22	56	0.009	1	1.82	0.003	0.03	0.1	0.19	3.3	0.3	<0.05	8	1.2
L134W 101 50 N	Soil			8	19	0.26	56	0.008	<1	2.25	0.004	0.04	0.1	0.19	2.4	0.2	<0.05	7	0.8
L134W 102 00 N	Soil			18	15	0.21	44	0.008	<1	2.51	0.004	0.04	0.2	0.30	2.1	0.2	0.07	7	1.4
L134W 102 50 N	Soil			16	15	0.28	59	0.005	<1	1.36	0.005	0.05	0.2	0.15	2.2	0.3	<0.05	7	1.4
L134W 103 00 N	Soil			30	21	0.24	42	0.008	<1	2.79	0.004	0.05	0.1	0.23	3.6	0.2	0.13	4	3.7
L134W 103 50 N	Soil			5	11	0.09	29	0.016	<1	1.01	0.003	0.04	0.1	0.07	1.0	0.2	<0.05	8	<0.5
L134W 104 00 N	Soil			6	14	0.11	43	0.010	1	1.21	0.003	0.05	0.2	0.08	0.9	0.2	<0.05	10	0.6
L134W 104 50 N	Soil			6	22	0.26	37	0.011	<1	1.90	0.005	0.05	0.2	0.15	2.7	0.3	<0.05	10	0.8
L134W 105 00 N	Soil			10	8	0.02	14	0.015	<1	CHECK	0.004	0.02	0.1	0.29	16.1	<0.1	0.08	3	3.6
L134W 105 50 N	Soil			6	15	0.21	53	0.006	<1	1.51	0.004	0.06	0.1	0.16	2.8	0.3	<0.05	5	6.9
L134W 106 00 N	Soil			28	15	0.28	168	0.005	2	1.18	0.006	0.08	0.1	0.07	1.5	0.2	0.05	5	4.2
L134W 106 50 N	Soil			7	11	0.11	88	0.006	<1	1.82	0.005	0.05	0.2	0.19	1.6	0.3	0.09	7	7.6
L134W 107 00 N	Soil			12	17	0.14	72	0.005	<1	1.46	0.004	0.06	0.1	0.10	2.0	0.2	0.06	8	5.0
L134W 107 50 N	Soil			7	15	0.16	49	0.002	<1	4.39	0.004	0.04	0.1	0.19	3.0	0.3	0.05	10	5.1
L134W 108 00 N	Soil			10	7	0.23	69	0.013	<1	6.82	0.003	0.03	<0.1	0.24	4.5	0.1	0.10	4	10.8
L134W 108 50 N	Soil			29	10	0.25	167	0.008	<1	1.61	0.008	0.10	<0.1	0.19	3.2	0.3	0.11	4	4.6
L134W 109 00 N	Soil			11	18	0.11	69	0.009	<1	2.00	0.006	0.05	0.2	0.23	1.2	0.2	0.05	9	0.5

This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.



AcmeLabs ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
Report Date: August 28, 2008

Page: 8 of 8 **Part** 1

CERTIFICATE OF ANALYSIS

SMI08000686.1

Method	Analyte	Unit	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
			Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	P
		MDL	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	%	
L134W	109 50 N	Soil	2.0	31.4	23.6	38	0.5	5.6	2.8	145	2.61	17.1	0.8	5.2	0.1	9	0.2	0.7	0.5	57	0.02	0.065
L134W	110 00 N	Soil	2.7	89.4	32.8	78	0.2	19.7	7.1	313	5.46	24.8	1.0	16.4	2.0	6	0.2	1.8	0.6	69	0.02	0.050
L134W	110 50 N	Soil	2.7	44.1	26.6	46	0.4	6.0	3.4	202	6.41	26.1	0.7	8.2	1.1	5	0.2	1.7	0.7	109	0.02	0.052
L134W	111 00 N	Soil	3.1	54.6	45.8	28	5.9	6.2	27.9	3341	2.43	8.5	4.2	5.9	0.2	10	0.1	0.9	0.2	29	0.10	0.363
L134W	111 50 N	Soil	1.8	46.5	32.8	90	0.3	14.1	8.9	1310	4.53	23.8	1.3	3.0	0.2	27	0.3	1.7	0.5	94	0.24	0.084
L134W	112 00 N	Soil	1.4	37.3	25.4	50	0.3	8.2	6.4	348	3.60	20.5	1.3	4.2	0.3	10	0.3	0.8	0.4	72	0.07	0.091



AcmeLabs ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
Report Date: August 28, 2008

Page: 8 of 8 **Part** 2

CERTIFICATE OF ANALYSIS

SMI08000686.1

Method	Analyte	Unit	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
			La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
			ppm	ppm	%	ppm	%	ppm	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
		MDL	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.05	1	0.5	
L134W	109 50 N	Soil	7	12	0.13	65	0.008	2	1.46	0.004	0.05	0.2	0.09	1.0	0.2	<0.05	8	<0.5
L134W	110 00 N	Soil	5	24	0.35	54	0.004	<1	2.53	0.004	0.05	0.1	0.16	3.5	0.1	0.05	6	1.1
L134W	110 50 N	Soil	5	16	0.10	34	0.018	<1	1.59	0.004	0.04	0.2	0.18	2.0	0.2	0.06	14	<0.5
L134W	111 00 N	Soil	10	21	0.13	56	0.005	<1	3.18	0.005	0.04	0.2	0.71	0.8	0.4	0.24	3	1.6
L134W	111 50 N	Soil	7	21	0.41	132	0.013	2	1.91	0.006	0.09	0.2	0.92	1.7	0.2	0.05	9	0.5
L134W	112 00 N	Soil	8	15	0.17	87	0.006	1	2.22	0.006	0.08	0.1	0.12	1.5	0.2	<0.05	8	0.9

QUALITY CONTROL REPORT

SMI08000686.1

Method Analyte Unit MDL	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
	Mo ppm 0.1	Cu ppm 0.1	Pb ppm 0.1	Zn ppm 1	Ag ppm 0.1	Ni ppm 0.1	Co ppm 0.1	Mn ppm 1	Fe % 0.01	As ppm 0.5	U ppm 0.1	Au ppb 0.5	Th ppm 0.1	Sr ppm 1	Cd ppm 0.1	Sb ppm 0.1	Bi ppm 0.1	V ppm 2	Ca % 0.01	P % 0.001	
Pulp Duplicates																					
L88W 118 00 N	Soil	1.3	35.1	58.1	107	0.2	12.4	6.5	513	4.86	25.7	1.3	5.9	0.3	21	0.4	2.0	0.3	122	0.09	0.066
REP L88W 118 00 N	QC	1.2	36.2	59.0	110	0.2	12.0	6.5	536	4.82	24.5	1.2	5.5	0.3	20	0.3	1.9	0.4	115	0.09	0.064
L88W 119 50 N	Soil	1.7	32.4	223.7	165	0.5	8.6	8.4	1302	5.80	36.0	1.6	10.0	0.6	15	0.3	2.2	1.6	76	0.12	0.189
REP L88W 119 50 N	QC	1.7	34.3	233.1	167	0.5	9.3	9.1	1489	5.97	39.0	1.6	13.7	0.5	15	0.3	2.6	1.6	78	0.12	0.201
L90W 108 00 N	Soil	2.0	24.4	29.1	48	0.7	6.7	3.8	209	5.75	27.9	0.7	24.4	0.7	12	<0.1	2.1	0.4	121	0.01	0.063
REP L90W 108 00 N	QC	2.1	24.6	29.8	47	0.7	6.6	3.7	213	5.81	29.5	0.7	5.1	0.8	8	<0.1	2.0	0.4	121	0.02	0.062
L130W 92 50 N	Soil	2.3	44.7	69.5	150	1.3	9.9	10.6	515	5.19	84.8	1.2	27.3	1.8	10	0.3	3.0	1.8	52	0.06	0.119
REP L130W 92 50 N	QC	2.2	46.2	71.5	158	1.4	10.4	10.8	508	5.16	88.6	1.3	23.8	1.7	10	0.4	3.1	1.6	54	0.07	0.123
L130W 105 50 N	Soil	3.1	63.5	68.6	104	2.0	10.3	6.1	337	5.13	92.0	2.2	21.2	0.9	13	0.4	2.5	1.5	77	0.04	0.129
REP L130W 105 50 N	QC	3.2	67.4	74.3	106	2.1	11.4	6.6	363	5.43	97.1	2.5	21.9	1.2	13	0.5	2.9	1.6	80	0.04	0.141
L132W 97 00 N	Soil	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.
REP L132W 97 00 N	QC	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.
L132W 104 00 N	Soil	4.5	49.0	74.4	93	0.7	11.2	6.2	395	6.28	58.6	0.9	13.6	1.5	8	0.2	2.3	1.0	83	0.02	0.111
REP L132W 104 00 N	QC	2.4	54.6	65.7	120	0.8	11.6	6.4	509	6.16	43.2	1.2	38.6	1.5	9	0.3	2.4	0.9	70	0.05	0.123
L132W 104 50 N	Soil	54.9	193.6	53.9	46	0.4	5.2	7.3	366	6.45	106.8	0.9	23.8	0.9	6	0.2	1.8	0.9	80	0.01	0.130
REP L132W 104 50 N	QC	56.6	189.1	52.1	47	0.4	5.6	7.4	372	6.59	110.8	0.9	26.7	1.0	6	0.1	1.6	0.9	81	0.01	0.144
L134W 97 50 N	Soil	2.0	39.1	59.4	90	0.4	7.2	3.8	216	3.79	37.9	0.8	7.6	1.4	7	0.3	1.2	0.8	47	0.02	0.050
REP L134W 97 50 N	QC	2.0	36.1	60.0	93	0.4	6.2	4.1	222	3.90	39.2	0.9	16.3	1.5	7	0.3	1.5	0.9	50	0.01	0.052
L134W 107 50 N	Soil	36.1	1102	26.8	37	0.9	4.8	9.3	144	6.27	10.5	1.3	151.2	2.3	5	0.2	0.8	0.5	81	0.04	0.121
REP L134W 107 50 N	QC	36.2	1098	26.9	36	0.9	5.0	8.9	143	6.26	10.3	1.1	178.1	2.3	4	0.1	0.8	0.5	79	0.04	0.114
Reference Materials																					
STD DS7	Standard	21.1	113.6	67.7	403	0.8	52.6	8.8	646	2.44	50.6	4.6	73.7	4.0	73	5.8	5.6	4.3	88	0.86	0.072
STD DS7	Standard	21.2	115.6	74.2	415	0.8	58.0	9.8	612	2.48	53.9	5.3	67.8	4.8	86	6.1	5.9	4.8	89	0.97	0.078
STD DS7	Standard	19.0	111.0	76.9	403	0.8	56.3	9.7	612	2.35	53.0	5.4	64.0	4.6	70	6.3	5.7	5.0	86	0.93	0.081
STD DS7	Standard	20.6	131.0	79.9	415	0.9	58.7	10.2	671	2.52	53.0	5.7	97.8	4.9	85	6.8	6.9	5.1	92	0.97	0.080
STD DS7	Standard	20.5	120.0	71.6	387	0.9	52.8	10.2	611	2.32	47.5	5.2	103.3	3.8	58	5.6	4.7	3.6	90	0.89	0.072
STD DS7	Standard	19.2	120.7	74.4	405	0.9	55.7	10.0	672	2.47	49.4	5.2	66.8	4.3	69	6.1	6.0	4.7	87	0.90	0.074
STD DS7 Expected		20.9	109	70.6	411	0.9	56	9.7	627	2.39	48.2	4.9	70	4.4	69	6.4	5.9	4.5	86	0.93	0.08

QUALITY CONTROL REPORT

SMI08000686.1

Method	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se	
Unit	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
MDL	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5	
Pulp Duplicates																	
L88W 118 00 N	Soil	6	20	0.25	140	0.039	4	1.61	0.006	0.09	0.2	0.08	2.5	0.2	<0.05	10	<0.5
REP L88W 118 00 N	QC	6	19	0.25	140	0.041	4	1.62	0.006	0.09	0.2	0.06	2.6	0.2	0.05	10	<0.5
L88W 119 50 N	Soil	11	15	0.18	56	0.009	3	1.38	0.004	0.07	0.2	0.05	1.6	0.2	0.08	7	0.8
REP L88W 119 50 N	QC	11	15	0.18	60	0.013	4	1.46	0.004	0.09	0.1	0.05	1.8	0.2	0.25	7	1.0
L90W 108 00 N	Soil	5	19	0.16	54	0.028	2	1.59	0.004	0.04	0.2	0.09	2.1	0.1	0.06	11	<0.5
REP L90W 108 00 N	QC	5	19	0.16	52	0.026	<1	1.58	0.005	0.04	0.2	0.10	2.2	0.1	<0.05	12	<0.5
L130W 92 50 N	Soil	10	18	0.17	45	0.011	1	3.82	0.005	0.03	0.2	0.37	3.6	0.2	<0.05	5	1.6
REP L130W 92 50 N	QC	10	19	0.17	46	0.011	1	3.96	0.005	0.04	0.2	0.37	3.7	0.2	<0.05	6	1.5
L130W 105 50 N	Soil	10	20	0.26	56	0.010	2	2.66	0.004	0.05	0.2	0.38	2.6	0.3	<0.05	7	1.4
REP L130W 105 50 N	QC	11	21	0.26	59	0.009	2	2.83	0.005	0.05	0.2	0.43	3.0	0.3	<0.05	8	1.8
L132W 97 00 N	Soil	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.
REP L132W 97 00 N	QC	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.
L132W 104 00 N	Soil	6	19	0.23	61	0.011	2	2.18	0.005	0.06	0.2	0.14	2.7	0.2	<0.05	9	0.8
REP L132W 104 00 N	QC	7	20	0.25	50	0.010	2	2.33	0.004	0.04	0.2	0.18	2.6	0.2	<0.05	7	0.7
L132W 104 50 N	Soil	5	8	0.18	43	0.006	2	1.70	0.004	0.07	0.1	0.10	2.0	0.5	<0.05	8	2.7
REP L132W 104 50 N	QC	5	7	0.20	45	0.007	<1	1.88	0.004	0.08	<0.1	0.11	2.0	0.5	0.06	9	2.8
L134W 97 50 N	Soil	7	10	0.12	48	0.008	<1	1.83	0.004	0.03	0.2	0.11	1.9	0.3	<0.05	6	<0.5
REP L134W 97 50 N	QC	7	10	0.12	47	0.007	<1	1.85	0.004	0.03	0.1	0.12	1.8	0.3	<0.05	6	1.4
L134W 107 50 N	Soil	7	15	0.16	49	0.002	<1	4.39	0.004	0.04	0.1	0.19	3.0	0.3	0.05	10	5.1
REP L134W 107 50 N	QC	7	15	0.16	51	0.002	<1	4.35	0.004	0.04	0.1	0.19	2.9	0.3	0.06	11	5.7
Reference Materials																	
STD DS7	Standard	12	162	1.08	404	0.119	41	1.04	0.087	0.45	4.1	0.19	2.3	4.4	0.21	5	3.6
STD DS7	Standard	14	203	1.06	383	0.135	41	1.02	0.099	0.46	3.8	0.22	3.0	4.2	0.21	5	3.4
STD DS7	Standard	12	196	1.03	347	0.117	38	1.01	0.093	0.45	3.4	0.20	2.7	4.2	0.21	5	3.1
STD DS7	Standard	13	183	1.08	391	0.145	39	1.08	0.089	0.51	4.1	0.18	2.6	4.5	0.21	5	3.7
STD DS7	Standard	12	161	1.07	405	0.122	37	1.04	0.074	0.46	3.8	0.19	2.6	4.2	0.19	5	2.8
STD DS7	Standard	11	169	1.09	389	0.126	39	1.04	0.073	0.51	4.0	0.19	2.2	4.3	0.20	5	3.1
STD DS7 Expected		13	163	1.05	370	0.124	39	0.959	0.073	0.44	3.8	0.2	2.5	4.2	0.21	5	3.5

QUALITY CONTROL REPORT

SMI08000686.1

		1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
		Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	P
		ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	%
		0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	0.001
BLK	Blank	<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01	<0.001
BLK	Blank	<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01	<0.001
BLK	Blank	<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01	<0.001
BLK	Blank	<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01	<0.001
BLK	Blank	<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01	<0.001
BLK	Blank	<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01	<0.001

QUALITY CONTROL REPORT

SMI08000686.1

		1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
		La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
		ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm
		1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5
BLK	Blank	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
BLK	Blank	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
BLK	Blank	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
BLK	Blank	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
BLK	Blank	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
BLK	Blank	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.

Vancouver BC V6C 1Z7 Canada

Submitted By:

Glen Garratt

Receiving Lab:

Canada-Smithers

Received:

August 08, 2008

Report Date:

August 28, 2008

Page:

1 of 3

CERTIFICATE OF ANALYSIS

SMI08000707.1

CLIENT JOB INFORMATION

Project: Zymo
Shipment ID: zy-so-08-04
P.O. Number
Number of Samples: 41

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
DISP-RJT-SOIL Immediate Disposal of Soil Reject

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Mincord Exploration Consultants Ltd.
110 - 325 Howe St.
Vancouver BC V6C 1Z7
Canada

CC: Bob Johnston

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status
SS80	41	Dry at 60C sieve 100g to -80 mesh		
Dry at 60C	41	Dry at 60C		
1DX15	40	1:1:1 Aqua Regia digestion ICP-MS analysis	15	Completed

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only. All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

ACME ANALYTICAL LABORATORIES LTD.

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.
Vancouver BC V6C 1Z7 Canada

Project:

Zymo

Report Date:

August 28, 2008

Page:

2 of 3

Part 1

CERTIFICATE OF ANALYSIS

SMI08000707.1

Method Analyte Unit MDL	1DX15																			
	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	P
	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	%
	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	0.1	2	0.01
L136W 92 00N Soil	1.5	40.4	49.6	165	0.3	9.8	5.8	492	5.94	81.7	0.7	20.8	0.2	34	0.5	3.0	1.8	75	0.38	0.074
L136W 92 50N Soil	1.4	41.3	32.6	124	0.4	10.3	5.5	328	4.61	73.8	0.5	4.9	0.2	14	0.3	3.2	1.2	83	0.11	0.066
L136W 93 00N Soil	2.2	60.2	58.9	251	1.0	14.1	10.8	2416	4.17	59.5	1.9	28.1	0.5	19	0.5	2.6	1.4	50	0.17	0.124
L136W 93 50N Soil	3.0	58.9	74.2	144	0.6	16.0	6.4	388	6.27	94.7	0.8	18.6	1.5	7	0.3	4.4	1.1	63	0.02	0.076
L136W 94 00N Soil	1.8	38.3	56.3	123	1.0	10.1	6.6	402	4.54	75.5	1.0	61.5	0.5	7	0.2	2.6	1.5	44	0.08	0.070
L136W 94 50N Soil	2.0	29.2	57.4	57	1.3	7.4	2.2	132	4.20	61.3	0.8	6.8	0.2	8	0.6	1.1	2.1	73	0.08	0.067
L136W 95 00N Soil	1.4	45.7	36.0	75	0.3	6.8	8.9	1517	5.67	102.4	0.4	10.9	0.3	5	0.4	2.4	2.1	63	0.02	0.115
L136W 95 50N Soil	2.3	46.3	45.0	86	0.5	13.4	6.2	406	5.17	70.5	0.7	12.0	0.6	7	0.5	2.8	0.8	64	0.02	0.050
L136W 96 00N Soil	1.0	14.2	17.9	33	0.5	3.9	1.4	71	1.47	27.0	0.4	21.2	0.2	5	<0.1	0.8	0.9	43	0.01	0.030
L136W 96 50N Soil	1.5	68.4	63.6	144	1.4	24.2	12.7	717	4.55	47.6	1.1	11.6	2.2	11	1.0	3.0	0.6	59	0.05	0.070
L136W 97 00N Soil	2.0	38.0	87.8	106	1.1	10.2	5.1	333	8.31	61.2	0.9	56.9	1.6	6	0.5	2.0	1.5	79	0.01	0.103
L136W 97 50N Soil	1.9	50.7	65.8	131	0.8	9.2	5.2	303	5.41	56.3	0.8	9.9	0.9	7	0.3	1.7	1.1	67	0.02	0.106
L136W 98 00N Soil	1.7	22.9	20.4	56	0.2	5.7	4.4	350	3.73	30.6	0.4	7.0	0.2	6	0.1	2.7	0.9	70	0.04	0.065
L136W 98 50N Soil	3.5	112.5	59.9	88	0.9	8.9	5.4	295	6.06	591.5	0.9	25.4	1.8	7	0.1	2.9	1.1	63	0.04	0.041
L136W 99 00N Soil	11.3	501.4	34.6	97	0.2	12.5	13.7	921	4.22	29.7	1.7	17.1	0.3	12	0.2	1.3	1.1	40	0.08	0.115
L136W 99 50N Soil	2.9	39.1	57.0	57	0.6	9.8	3.7	241	4.51	28.6	0.7	8.0	0.4	8	0.2	1.5	0.6	63	0.02	0.067
L136W 100 00N Soil	16.0	156.1	49.2	47	0.8	7.4	4.2	312	6.09	186.1	0.8	23.6	0.3	8	0.3	1.2	0.7	74	0.03	0.131
L136W 100 50N Soil	2.0	646.8	44.4	52	0.4	11.4	4.8	225	2.88	23.7	1.8	12.6	0.2	8	<0.1	1.2	0.6	56	0.02	0.061
L136W 101 00N Soil	2.5	69.1	33.9	66	0.5	15.7	7.2	356	4.07	20.3	0.9	6.8	0.4	7	0.2	2.1	0.5	60	0.03	0.071
L136W 101 50N Soil	4.7	37.1	15.3	14	0.4	7.7	1.4	65	2.54	12.5	0.6	47.0	0.6	6	<0.1	0.4	0.6	56	0.01	0.056
L136W 102 00N Soil	2.2	151.4	74.8	90	2.4	14.2	4.9	103	1.03	15.1	5.6	12.4	0.3	15	0.2	0.7	0.5	26	0.06	0.112
L136W 102 50N Soil	4.1	47.3	59.9	49	0.4	7.4	3.5	185	3.84	24.5	1.1	18.1	0.9	5	0.2	1.2	1.0	57	0.02	0.063
L136W 103 00N Soil	8.3	110.8	111.8	140	0.5	16.3	16.8	955	7.18	64.2	1.0	25.9	2.1	7	0.2	3.5	1.0	61	0.07	0.145
L136W 103 50N Soil	8.1	357.8	69.1	79	2.6	12.0	6.0	177	4.63	34.6	1.5	19.5	0.6	9	0.3	1.7	0.8	61	0.05	0.100
L136W 104 00N Soil	3.7	52.2	42.2	66	0.5	9.4	4.2	243	4.17	33.5	0.7	7.6	0.2	10	0.2	2.7	1.0	76	0.02	0.087
L136W 104 50N Soil	22.0	118.1	46.9	54	0.4	8.7	9.9	493	4.45	39.3	1.1	9.1	0.2	7	0.3	1.6	0.8	68	0.01	0.097
L136W 105 00N Soil	11.7	62.2	37.4	36	1.0	8.2	2.7	158	2.66	23.9	0.7	38.7	0.2	13	0.3	0.8	0.8	42	0.03	0.081
L136W 105 50N Soil	29.1	268.1	32.2	38	0.8	7.8	4.0	142	4.34	20.0	1.1	16.3	0.2	18	0.3	0.9	0.5	67	0.04	0.062
L136W 106 00N Soil	28.4	320.0	57.7	70	0.2	12.4	7.9	210	5.98	35.2	0.6	97.6	2.2	5	0.3	1.6	0.9	54	0.03	0.064
L136W 106 50N Soil	11.2	312.6	28.8	42	0.4	11.3	5.0	289	4.36	25.5	0.7	47.9	0.5	6	0.2	1.6	0.7	66	0.03	0.058



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
 Report Date: August 28, 2008

Page: 2 of 3 Part 2

CERTIFICATE OF ANALYSIS

SMI08000707.1

Method	Analyte	Unit	MDL	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
				La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
				ppm	ppm	%	ppm	%	ppm	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
				1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.05	1	0.5	
L136W 92 00N	Soil			10	16	0.17	118	0.010	<1	1.15	0.005	0.05	0.1	0.19	1.7	0.2	<0.05	7	0.6
L136W 92 50N	Soil			8	16	0.08	83	0.012	1	0.89	0.005	0.05	<0.1	0.05	1.5	0.2	<0.05	8	<0.5
L136W 93 00N	Soil			14	19	0.28	93	0.006	<1	2.02	0.006	0.05	0.2	0.24	2.4	0.3	<0.05	5	0.6
L136W 93 50N	Soil			5	24	0.26	56	0.005	<1	2.09	0.004	0.05	0.1	0.20	2.8	0.3	<0.05	7	1.1
L136W 94 00N	Soil			9	13	0.14	45	0.004	<1	1.55	0.005	0.03	0.2	0.22	1.7	0.2	<0.05	5	1.2
L136W 94 50N	Soil			7	16	0.11	45	0.005	<1	1.39	0.005	0.04	0.2	0.11	1.0	0.1	<0.05	8	<0.5
L136W 95 00N	Soil			8	13	0.05	110	0.007	1	0.76	0.002	0.05	0.1	0.05	1.5	0.2	<0.05	5	0.6
L136W 95 50N	Soil			5	24	0.23	47	0.009	1	1.58	0.004	0.04	0.2	0.09	2.4	0.2	<0.05	7	0.9
L136W 96 00N	Soil			9	9	0.03	29	0.005	<1	0.81	0.003	0.03	<0.1	0.19	0.6	0.3	<0.05	6	<0.5
L136W 96 50N	Soil			7	27	0.40	81	0.005	2	3.02	0.007	0.07	0.1	0.33	4.6	0.2	<0.05	6	1.0
L136W 97 00N	Soil			7	19	0.18	56	0.010	1	1.98	0.004	0.04	0.1	0.12	2.6	0.2	<0.05	10	0.9
L136W 97 50N	Soil			7	16	0.17	50	0.005	1	1.61	0.005	0.04	0.1	0.13	2.2	0.3	<0.05	6	<0.5
L136W 98 00N	Soil			9	11	0.06	37	0.006	2	0.91	0.003	0.04	0.1	0.10	1.0	0.2	<0.05	7	<0.5
L136W 98 50N	Soil			6	18	0.16	47	0.005	<1	1.80	0.004	0.05	0.2	0.17	2.3	0.4	<0.05	7	1.1
L136W 99 00N	Soil			12	14	0.32	52	0.007	<1	2.16	0.006	0.05	0.2	0.09	1.6	0.1	<0.05	6	1.9
L136W 99 50N	Soil			5	21	0.15	58	0.007	1	1.87	0.004	0.04	0.2	0.16	1.6	0.2	<0.05	8	0.7
L136W 100 00N	Soil			6	17	0.14	45	0.011	<1	1.71	0.005	0.05	0.3	0.11	1.2	0.2	<0.05	10	<0.5
L136W 100 50N	Soil			16	19	0.31	40	0.007	<1	2.26	0.005	0.07	0.2	0.11	2.5	0.2	<0.05	7	0.8
L136W 101 00N	Soil			6	20	0.30	47	0.006	2	1.78	0.004	0.05	0.2	0.13	1.9	0.1	<0.05	6	1.1
L136W 101 50N	Soil			6	19	0.09	46	0.006	<1	1.43	0.004	0.03	0.1	0.07	0.8	0.3	<0.05	11	0.7
L136W 102 00N	Soil			26	22	0.20	61	0.009	2	2.78	0.008	0.04	0.3	0.37	1.1	0.3	<0.05	9	0.9
L136W 102 50N	Soil			7	19	0.13	34	0.005	<1	1.87	0.003	0.03	0.2	0.14	1.6	0.2	<0.05	8	1.5
L136W 103 00N	Soil			6	22	0.25	49	0.005	<1	2.27	0.003	0.04	0.1	0.20	2.7	0.2	<0.05	5	3.4
L136W 103 50N	Soil			17	18	0.20	36	0.005	<1	1.92	0.004	0.04	0.2	0.25	1.4	0.3	<0.05	7	1.9
L136W 104 00N	Soil			5	17	0.15	59	0.008	<1	1.58	0.005	0.05	0.2	0.10	1.0	0.3	<0.05	7	1.3
L136W 104 50N	Soil			11	17	0.13	38	0.008	<1	1.32	0.003	0.05	0.1	0.07	0.6	0.3	<0.05	9	1.6
L136W 105 00N	Soil			7	19	0.11	58	0.005	<1	1.23	0.004	0.07	<0.1	0.08	0.5	0.3	<0.05	6	0.9
L136W 105 50N	Soil			9	17	0.17	55	0.007	<1	1.51	0.006	0.04	0.1	0.11	0.9	0.3	<0.05	9	1.8
L136W 106 00N	Soil			5	18	0.23	41	0.002	<1	2.83	0.004	0.06	0.1	0.14	2.5	0.4	<0.05	6	3.0
L136W 106 50N	Soil			6	21	0.19	47	0.006	<1	1.88	0.004	0.05	0.2	0.08	1.7	0.3	<0.05	11	0.6

This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.



AcmeLabs ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
Report Date: August 28, 2008

Page: 3 of 3 **Part** 1

CERTIFICATE OF ANALYSIS

SMI08000707.1

Method	Analyte	Unit	MDL	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
				Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	P
				ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	%
				0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	0.001
L136W	107	00N	Soil	35.3	2956	25.2	29	0.6	5.6	5.9	406	3.66	22.5	1.9	255.6	4.5	24	0.3	9.4	0.6	49	0.19	0.093
L136W	107	50N	Soil	64.0	469.6	5.4	38	0.7	2.9	3.4	73	3.01	51.3	2.0	133.6	6.0	4	<0.1	2.1	0.2	42	0.01	0.074
L136W	108	00N	Soil	79.3	826.4	35.6	63	0.6	8.4	7.1	801	3.34	84.2	2.3	104.4	0.7	11	0.3	5.1	0.8	50	0.04	0.093
L136W	108	50N	Soil	27.9	590.9	19.0	29	0.5	3.4	3.2	190	3.12	81.2	1.6	236.6	3.8	8	0.3	4.0	0.4	37	0.02	0.082
L136W	109	00N	Soil	66.9	1858	51.1	80	0.5	15.0	9.0	540	8.58	73.4	5.7	31.7	0.8	71	0.2	4.6	1.1	91	0.26	0.097
L136W	109	50N	Soil	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.
L136W	110	00N	Soil	2.3	75.1	30.7	73	0.4	17.4	5.2	247	6.26	27.4	0.5	7.0	1.0	6	<0.1	1.4	0.5	88	0.02	0.067
L136W	110	50N	Soil	2.3	63.2	22.9	78	<0.1	12.2	4.4	202	5.40	25.5	0.4	3.8	1.2	6	<0.1	1.5	0.6	96	0.02	0.074
L136W	111	00N	Soil	2.3	53.9	49.6	70	0.3	10.9	8.1	798	9.28	31.3	0.9	22.3	2.7	5	0.1	1.3	0.9	93	0.02	0.065
L136W	111	50N	Soil	1.9	39.4	26.7	77	0.4	19.6	7.1	281	5.18	19.4	1.3	2.4	0.8	12	0.2	0.9	0.4	76	0.07	0.062
L136W	112	00N	Soil	2.1	54.7	27.2	74	0.1	11.8	5.1	323	5.20	18.3	0.8	5.3	1.3	7	0.2	1.1	0.5	79	0.03	0.079



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
 Report Date: August 28, 2008

Page: 3 of 3 Part 2

CERTIFICATE OF ANALYSIS

SMI08000707.1

Method	Analyte	Unit	MDL	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15		
				La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
				ppm	ppm	%	ppm	%	ppm	%	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	
				1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.05	1	0.5	
L136W 107 00N	Soil			13	10	0.09	243	0.002	<1	1.70	0.003	0.06	<0.1	0.10	1.3	0.4	<0.05	6	1.4
L136W 107 50N	Soil			5	4	0.03	17	<0.001	<1	0.83	0.002	0.09	<0.1	0.10	1.5	0.4	<0.05	3	0.7
L136W 108 00N	Soil			10	14	0.08	141	0.003	<1	1.01	0.003	0.05	0.1	0.16	1.0	0.4	<0.05	5	1.0
L136W 108 50N	Soil			6	6	0.04	61	0.002	1	1.26	0.003	0.06	<0.1	0.12	1.4	0.4	<0.05	4	0.9
L136W 109 00N	Soil			25	29	0.25	282	0.011	<1	2.37	0.005	0.05	0.2	0.34	2.6	0.2	<0.05	12	3.0
L136W 109 50N	Soil			I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.
L136W 110 00N	Soil			4	29	0.22	51	0.004	<1	2.10	0.003	0.04	<0.1	0.11	2.9	0.2	<0.05	8	0.6
L136W 110 50N	Soil			4	22	0.12	36	0.008	1	1.50	0.004	0.03	<0.1	0.10	2.6	0.2	<0.05	9	0.6
L136W 111 00N	Soil			5	29	0.16	43	0.010	<1	3.20	0.005	0.03	0.1	0.13	3.4	0.2	<0.05	10	0.7
L136W 111 50N	Soil			6	27	0.32	94	0.006	<1	2.65	0.005	0.05	0.1	0.12	3.4	0.2	<0.05	11	1.0
L136W 112 00N	Soil			5	27	0.17	53	0.013	2	2.57	0.004	0.05	0.2	0.15	2.5	0.2	<0.05	10	1.1

QUALITY CONTROL REPORT

SMI08000707.1

Method	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	P	
Unit	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	%	
MDL	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	0.001	
Pulp Duplicates																					
L136W 95 50N	Soil	2.3	46.3	45.0	86	0.5	13.4	6.2	406	5.17	70.5	0.7	12.0	0.6	7	0.5	2.8	0.8	64	0.02	0.050
REP L136W 95 50N	QC	2.5	48.1	46.1	83	0.4	13.1	6.3	402	5.16	69.3	0.7	11.3	0.7	7	0.7	2.8	0.7	63	0.02	0.050
L136W 106 50N	Soil	11.2	312.6	28.8	42	0.4	11.3	5.0	289	4.36	25.5	0.7	47.9	0.5	6	0.2	1.6	0.7	66	0.03	0.058
REP L136W 106 50N	QC	12.1	315.2	29.6	40	0.4	11.3	4.5	281	4.19	26.1	0.7	116.1	0.5	6	0.2	1.6	0.8	67	0.03	0.057
Reference Materials																					
STD DS7	Standard	21.0	123.3	79.9	431	0.9	62.1	10.5	681	2.59	54.2	5.5	66.4	4.4	75	6.5	6.6	4.8	93	1.01	0.078
STD DS7	Standard	18.3	106.8	71.4	399	0.8	55.3	8.8	609	2.36	52.3	4.9	67.2	4.0	70	6.2	6.1	4.8	83	0.91	0.079
STD DS7 Expected		20.9	109	70.6	411	0.9	56	9.7	627	2.39	48.2	4.9	70	4.4	69	6.4	5.9	4.5	86	0.93	0.08
BLK	Blank	<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01	<0.001
BLK	Blank	<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01	<0.001

QUALITY CONTROL REPORT

SMI08000707.1

Method	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se	
Unit	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
MDL	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5	
Pulp Duplicates																	
L136W 95 50N	Soil	5	24	0.23	47	0.009	1	1.58	0.004	0.04	0.2	0.09	2.4	0.2	<0.05	7	0.9
REP L136W 95 50N	QC	5	22	0.22	47	0.008	<1	1.53	0.004	0.04	0.1	0.07	2.2	0.2	<0.05	7	0.9
L136W 106 50N	Soil	6	21	0.19	47	0.006	<1	1.88	0.004	0.05	0.2	0.08	1.7	0.3	<0.05	11	0.6
REP L136W 106 50N	QC	7	21	0.19	47	0.006	<1	1.91	0.004	0.05	0.2	0.09	1.7	0.3	<0.05	10	0.9
Reference Materials																	
STD DS7	Standard	13	186	1.07	404	0.130	38	1.02	0.077	0.47	4.2	0.21	2.1	4.2	0.20	5	3.4
STD DS7	Standard	11	161	1.05	356	0.110	41	0.96	0.084	0.45	3.9	0.20	2.1	4.3	0.19	4	3.2
STD DS7 Expected		13	163	1.05	370	0.124	39	0.959	0.073	0.44	3.8	0.2	2.5	4.2	0.21	5	3.5
BLK	Blank	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
BLK	Blank	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.

Vancouver BC V6C 1Z7 Canada

Submitted By:

Glen Garratt

Receiving Lab:

Canada-Smithers

Received:

August 08, 2008

Report Date:

September 02, 2008

Page:

1 of 2

CERTIFICATE OF ANALYSIS

SMI08000708.1

CLIENT JOB INFORMATION

Project: Zymo
Shipment ID: zy-rk-08-10
P.O. Number
Number of Samples: 12

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
DISP-RJT Dispose of Reject After 90 days

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Mincord Exploration Consultants Ltd.
110 - 325 Howe St.
Vancouver BC V6C 1Z7
Canada

CC: Bob Johnston

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status
R150	12	Crush, split and pulverize rock to 200 mesh		
1DX15	12	1:1:1 Aqua Regia digestion ICP-MS analysis	15	Completed

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only. All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
Report Date: September 02, 2008

Page: 2 of 2 **Part** 1

CERTIFICATE OF ANALYSIS

SMI08000708.1

Method	Analyte	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca
Unit		kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%
MDL		0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01
726683	Rock	2.07	34.9	1188	5.1	54	0.7	9.7	28.0	157	6.29	2.9	0.8	173.2	4.1	47	<0.1	0.6	0.6	92	0.58
726684	Rock	1.95	2.0	109.6	6.4	32	0.1	10.6	11.5	592	4.55	<0.5	0.2	5.2	0.9	15	<0.1	<0.1	0.5	62	0.17
726685	Rock	2.02	6.7	65.9	27.6	15	0.1	2.7	2.6	138	4.13	1.8	0.3	60.3	1.1	7	<0.1	0.6	1.6	23	0.01
726686	Rock	2.17	38.3	78.3	12.2	29	<0.1	5.9	5.2	105	3.04	1.5	0.2	12.0	1.7	10	0.2	<0.1	0.4	25	0.07
726687	Rock	1.77	5.0	105.3	6.5	40	<0.1	9.0	7.4	210	2.31	2.3	0.2	12.8	1.3	7	0.2	0.4	0.2	29	0.09
726688	Rock	2.30	9.7	723.6	45.9	44	0.4	11.2	19.5	262	6.09	6.6	0.4	57.3	1.1	9	<0.1	0.5	0.4	42	0.09
726689	Rock	2.22	12.8	232.7	32.0	57	0.2	7.7	10.9	308	3.08	2.5	0.2	20.2	1.2	7	0.2	0.1	0.2	23	0.07
726690	Rock	2.26	26.0	282.0	22.4	65	0.1	9.0	8.6	835	1.77	0.9	0.3	20.9	1.4	19	0.2	<0.1	0.2	34	0.55
726691	Rock	3.06	8.2	2280	7.1	76	0.6	11.6	27.1	470	4.70	5.0	2.1	129.8	6.1	32	0.3	0.2	0.4	84	0.87
726692	Rock	2.05	7.0	1694	4.2	79	0.5	10.0	18.3	498	4.96	1.2	0.7	144.3	5.5	23	0.2	<0.1	0.1	94	0.55
726693	Rock	2.41	11.0	2286	12.3	56	1.0	7.2	9.5	471	3.24	0.9	0.4	183.7	2.0	26	0.2	<0.1	0.3	62	0.27
726694	Rock	2.53	13.3	573.5	23.3	50	0.4	4.9	9.1	408	1.79	27.6	9.8	90.5	8.2	63	0.3	1.6	<0.1	27	1.17



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.

Vancouver BC V6C 1Z7 Canada

Project:

Zymo

Report Date:

September 02, 2008

Page:

2 of 2

Part 2

CERTIFICATE OF ANALYSIS

SMI08000708.1

Method	Analyte	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
		P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
Unit		%	ppm	ppm	%	ppm	%	ppm	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
MDL		0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.05	1	0.5	
726683	Rock	0.168	10	11	1.52	45	0.068	1	2.44	0.104	0.43	<0.1	0.04	6.6	0.7	1.95	10	2.3
726684	Rock	0.013	3	10	0.72	121	0.032	2	2.74	0.052	0.38	<0.1	<0.01	7.4	0.4	0.55	6	<0.5
726685	Rock	0.025	7	4	0.26	162	0.004	1	1.16	0.027	0.48	<0.1	0.02	3.2	0.6	0.26	4	2.7
726686	Rock	0.035	7	5	0.28	60	<0.001	<1	1.14	0.089	0.20	<0.1	0.11	2.9	0.3	0.16	3	3.1
726687	Rock	0.054	4	6	0.52	144	0.004	1	1.58	0.058	0.41	<0.1	0.02	3.6	0.5	0.16	3	1.1
726688	Rock	0.108	4	5	0.60	47	0.002	2	1.68	0.030	0.31	<0.1	0.05	5.8	0.4	1.83	4	10.0
726689	Rock	0.043	5	6	0.59	153	0.001	1	1.51	0.026	0.38	<0.1	0.05	3.2	0.4	0.94	3	3.0
726690	Rock	0.048	7	8	0.64	265	0.004	<1	1.74	0.050	0.52	<0.1	0.04	4.7	0.5	0.27	4	0.7
726691	Rock	0.179	21	7	1.07	160	0.081	2	1.79	0.043	0.66	<0.1	0.08	8.4	0.7	0.89	6	2.8
726692	Rock	0.180	19	8	1.20	170	0.106	1	1.92	0.080	0.80	<0.1	0.10	7.9	0.7	0.15	7	1.4
726693	Rock	0.014	4	12	0.54	195	0.007	<1	0.91	0.044	0.25	<0.1	0.16	5.3	0.2	0.52	5	1.0
726694	Rock	0.162	15	4	0.22	263	<0.001	3	0.73	0.007	0.27	<0.1	0.70	3.4	1.7	0.36	<1	0.5

QUALITY CONTROL REPORT

SMI08000708.1

Method	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
Unit	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	
MDL	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	
Reference Materials																					
STD DS7	Standard	18.5	113.5	74.9	403	0.8	54.6	9.9	670	2.51	49.1	5.3	82.4	4.5	68	6.0	6.1	4.8	86	0.90	
STD DS7	Standard	21.7	121.7	78.4	409	0.9	58.6	9.8	673	2.54	50.2	5.7	68.9	4.8	78	6.3	6.3	4.8	88	0.95	
STD DS7 Expected		20.9	109	70.6	411	0.9	56	9.7	627	2.39	48.2	4.9	70	4.4	69	6.4	5.9	4.5	86	0.93	
BLK	Blank	<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01	
Prep Wash																					
G1	Prep Blank	<0.01	1.0	2.4	2.8	50	<0.1	9.1	4.6	589	1.90	<0.5	2.7	0.6	4.5	63	<0.1	<0.1	<0.1	38	0.46
G1	Prep Blank	<0.01	0.6	2.4	2.9	48	<0.1	7.7	4.5	578	1.92	<0.5	3.0	<0.5	4.7	60	<0.1	<0.1	<0.1	38	0.47

QUALITY CONTROL REPORT

SMI08000708.1

Method		1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte		P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
Unit		%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm
MDL		0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5
Reference Materials																		
STD DS7	Standard	0.074	12	161	1.07	382	0.125	40	1.04	0.076	0.50	3.9	0.20	2.3	4.1	0.19	5	3.8
STD DS7	Standard	0.073	13	168	1.10	420	0.139	39	1.10	0.087	0.51	4.0	0.21	2.6	4.4	0.19	5	3.4
STD DS7 Expected		0.08	13	163	1.05	370	0.124	39	0.959	0.073	0.44	3.8	0.2	2.5	4.2	0.21	4.6	3.5
BLK	Blank	<0.001	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
Prep Wash																		
G1	Prep Blank	0.077	7	13	0.62	230	0.121	1	1.13	0.077	0.57	0.4	<0.01	2.6	0.4	<0.05	4	<0.5
G1	Prep Blank	0.078	8	12	0.61	223	0.122	1	1.12	0.088	0.55	0.2	<0.01	2.6	0.4	<0.05	5	<0.5



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.

Vancouver BC V6C 1Z7 Canada

Submitted By:

Glen Garratt

Receiving Lab:

Canada-Smithers

Received:

August 09, 2008

Report Date:

September 02, 2008

Page:

1 of 4

CERTIFICATE OF ANALYSIS

SMI08000715.1

CLIENT JOB INFORMATION

Project: Zymo
Shipment ID: zy-so-08-05
P.O. Number
Number of Samples: 78

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
DISP-RJT-SOIL Immediate Disposal of Soil Reject

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Mincord Exploration Consultants Ltd.
110 - 325 Howe St.
Vancouver BC V6C 1Z7
Canada

CC: Bob Johnston

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status
SS80	78	Dry at 60C sieve 100g to -80 mesh		
Dry at 60C	78	Dry at 60C		
1DX15	77	1:1:1 Aqua Regia digestion ICP-MS analysis	15	Completed

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only. All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

ACME ANALYTICAL LABORATORIES LTD.

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project:

Zymo

Report Date:

September 02, 2008

Page:

2 of 4

Part 1

CERTIFICATE OF ANALYSIS

SMI08000715.1

Method	Analyte	Unit	MDL	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15		
				Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	P
				ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	%		
				0.1	0.1	0.1	1	0.1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	2	0.01	0.001
L138W 9000 N	Soil			1.9	46.0	62.9	144	0.3	14.1	9.8	924	4.86	64.2	1.0	33.8	0.3	11	0.2	3.1	0.7	66	0.04	0.187
L138W 9050 N	Soil			1.4	52.9	58.8	154	0.8	17.7	10.0	2530	4.13	39.9	1.0	6.0	0.3	17	0.8	2.2	0.5	55	0.10	0.171
L138W 9100 N	Soil			1.7	40.2	67.3	95	0.3	9.0	4.5	384	4.69	58.1	0.8	5.7	0.2	10	0.2	2.9	1.0	75	0.05	0.206
L138W 9150 N	Soil			1.5	29.4	72.6	140	0.3	6.9	7.3	1690	4.37	65.6	0.7	12.7	0.2	10	0.4	2.9	1.4	64	0.05	0.078
L138W 9200 N	Soil			1.2	32.5	53.0	90	0.3	6.6	4.1	514	4.50	50.9	0.6	3.6	0.1	9	0.4	2.6	1.1	75	0.02	0.105
L138W 9250 N	Soil			2.2	44.0	233.2	157	1.1	6.7	8.9	2975	3.42	46.9	1.2	17.8	0.1	21	0.5	2.1	0.7	57	0.13	0.087
L138W 9300 N	Soil			7.9	71.2	101.1	128	0.7	9.6	11.4	594	11.03	110.9	1.2	8.3	0.3	37	0.3	12.3	2.7	36	0.47	0.160
L138W 9400 N	Soil			3.7	44.2	25.9	148	0.3	7.8	6.2	306	3.65	44.8	0.4	9.4	<0.1	37	0.3	3.4	3.2	63	0.41	0.059
L138W 9450 N	Soil			2.1	113.0	105.7	200	1.0	10.4	16.0	1729	5.86	68.9	1.6	19.1	0.3	32	0.5	3.2	1.9	54	0.30	0.144
L138W 9500 N	Soil			3.7	108.2	67.0	141	1.5	9.5	8.6	867	5.54	66.6	1.7	46.7	0.3	33	0.6	2.5	2.0	47	0.29	0.118
L138W 9550 N	Soil			2.9	84.0	53.9	158	1.6	15.4	7.1	311	4.02	51.9	2.0	29.1	0.3	23	0.4	1.7	2.9	48	0.19	0.105
L138W 9600 N	Soil			2.3	77.0	39.2	109	3.1	8.6	6.3	383	1.35	8.6	2.4	7.8	0.4	28	0.3	1.2	0.5	27	0.27	0.237
L138W 9650 N	Soil			5.6	38.4	43.5	94	0.3	6.7	4.9	394	6.75	81.7	0.7	6.6	0.5	6	0.3	1.8	1.1	100	0.02	0.098
L138W 9750 N	Soil			4.1	233.5	82.1	76	0.1	8.5	7.1	163	3.34	69.2	1.1	12.9	0.8	15	0.1	1.7	1.1	69	0.05	0.075
L138W 9800 N	Soil			24.6	589.7	112.8	109	0.1	24.3	44.0	599	7.10	313.5	2.7	12.2	2.2	59	0.2	2.7	1.5	68	0.17	0.072
L138W 9850 N	Soil			5.1	195.6	59.1	72	1.0	6.8	4.4	228	4.93	370.5	1.7	12.8	0.1	11	0.6	1.8	1.2	60	0.06	0.104
L138W 9900 N	Soil			5.5	119.8	79.7	102	0.9	9.0	12.4	2259	7.10	210.3	0.7	36.9	0.3	9	0.3	2.6	1.5	63	0.04	0.161
L138W 9950 N	Soil			16.6	136.2	13.7	18	0.6	3.2	3.1	265	4.40	8.6	0.8	56.6	0.2	11	0.2	0.4	0.5	104	0.05	0.134
L138W 10000 N	Soil			10.3	130.9	50.7	36	0.6	5.4	3.5	179	8.54	38.0	1.1	40.0	0.3	5	0.1	1.3	0.7	97	0.03	0.150
L138W 10050 N	Soil			7.1	97.7	81.8	92	0.2	13.8	9.8	521	6.90	35.8	0.9	10.2	0.5	8	0.3	2.2	0.7	77	0.02	0.222
L138W 10100 N	Soil			3.1	216.6	54.2	59	1.5	10.7	5.9	313	4.51	19.0	2.8	4.0	0.2	15	0.1	1.2	0.4	75	0.06	0.066
L138W 10200 N	Soil			16.2	176.3	47.5	80	0.4	9.8	48.3	2550	3.91	40.9	1.5	41.7	0.2	26	0.3	1.1	5.4	51	0.08	0.101
L138W 10250 N	Soil			I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.
L138W 10300 N	Soil			2.9	663.4	42.2	36	1.1	9.6	5.3	116	1.15	13.7	6.4	13.7	0.8	34	<0.1	0.4	0.4	17	0.10	0.280
L138W 10350 N	Soil			4.2	65.8	60.0	88	0.2	10.1	5.4	295	7.03	43.5	1.1	8.5	0.4	9	0.2	2.3	0.8	99	0.02	0.069
L138W 10400 N	Soil			52.2	341.7	65.1	69	0.5	8.7	9.1	452	4.79	33.5	1.3	35.3	0.5	11	0.2	1.5	0.9	57	0.04	0.096
L138W 10450 N	Soil			41.4	831.3	64.7	146	0.1	14.6	24.9	667	4.66	54.3	1.1	16.9	0.3	76	<0.1	2.3	1.5	83	0.41	0.056
L138W 10500 N	Soil			21.7	240.7	56.6	128	0.2	14.4	11.2	685	4.00	42.1	1.3	25.2	0.4	46	0.3	2.4	1.1	74	0.16	0.052
L138W 10550 N	Soil			11.2	215.1	5.2	6	0.3	5.8	0.7	48	2.55	18.0	0.6	4.8	0.3	200	1.1	0.4	0.1	16	0.83	0.062
L138W 10600 N	Soil			117.1	154.8	32.8	25	<0.1	4.4	11.3	341	6.05	21.4	0.8	12.7	0.1	13	<0.1	0.5	0.7	48	0.03	0.154

This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.



AcmeLabs ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
Report Date: September 02, 2008

Page: 2 of 4 **Part** 2

CERTIFICATE OF ANALYSIS

SMI08000715.1

Method	Analyte	Unit	MDL	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
				La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
				ppm	ppm	%	ppm	%	ppm	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
				1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.05	1	0.5	
L138W 9000 N	Soil			7	17	0.23	52	0.009	3	1.48	0.004	0.07	<0.1	0.08	1.8	0.2	0.06	6	0.5
L138W 9050 N	Soil			14	15	0.18	215	0.009	3	1.60	0.006	0.06	0.1	0.34	5.3	0.2	0.05	5	0.8
L138W 9100 N	Soil			6	15	0.09	52	0.019	3	0.97	0.004	0.06	0.1	0.10	1.4	0.1	<0.05	8	<0.5
L138W 9150 N	Soil			7	12	0.07	78	0.006	1	1.13	0.005	0.04	0.1	0.07	1.0	0.2	<0.05	7	<0.5
L138W 9200 N	Soil			7	14	0.08	81	0.011	2	1.00	0.004	0.05	0.2	0.05	0.9	0.2	<0.05	9	<0.5
L138W 9250 N	Soil			8	13	0.08	74	0.008	1	1.55	0.005	0.05	0.1	0.29	0.9	0.3	<0.05	6	0.9
L138W 9300 N	Soil			8	10	0.06	125	0.006	<1	1.71	0.006	0.04	0.2	0.16	1.5	0.1	0.06	5	1.8
L138W 9400 N	Soil			10	7	0.05	141	0.004	2	0.71	0.004	0.03	0.2	0.06	1.1	0.1	<0.05	5	<0.5
L138W 9450 N	Soil			16	12	0.13	114	0.006	<1	1.65	0.005	0.05	0.1	0.13	1.6	0.2	<0.05	6	1.3
L138W 9500 N	Soil			15	12	0.15	118	0.008	1	1.51	0.006	0.05	0.2	0.15	1.7	0.2	<0.05	6	2.1
L138W 9550 N	Soil			15	18	0.31	77	0.006	1	2.18	0.005	0.05	0.1	0.20	1.5	0.1	<0.05	8	1.2
L138W 9600 N	Soil			38	17	0.22	130	0.006	2	2.18	0.007	0.05	<0.1	0.24	3.3	0.2	0.14	4	2.1
L138W 9650 N	Soil			7	14	0.11	38	0.013	1	1.33	0.003	0.04	0.2	0.10	1.8	0.2	<0.05	13	0.7
L138W 9750 N	Soil			16	17	0.23	89	0.003	1	1.91	0.007	0.04	0.1	0.14	2.0	0.3	0.06	6	1.3
L138W 9800 N	Soil			23	20	0.32	234	0.003	2	2.94	0.009	0.05	<0.1	0.09	5.0	0.3	0.06	5	2.9
L138W 9850 N	Soil			9	11	0.15	50	0.007	<1	1.83	0.004	0.05	0.2	0.18	0.9	0.2	0.07	7	1.4
L138W 9900 N	Soil			5	14	0.18	75	0.005	2	1.34	0.004	0.04	0.1	0.18	1.4	0.3	<0.05	7	1.7
L138W 9950 N	Soil			5	7	0.22	53	0.011	1	2.12	0.005	0.04	0.2	0.16	1.1	0.3	<0.05	12	1.7
L138W 10000 N	Soil			4	19	0.32	32	0.020	1	2.64	0.005	0.05	0.2	0.23	2.3	0.2	0.06	11	2.7
L138W 10050 N	Soil			4	20	0.31	35	0.008	1	1.79	0.004	0.07	0.2	0.12	1.9	0.3	<0.05	8	1.9
L138W 10100 N	Soil			25	16	0.34	55	0.013	2	2.12	0.006	0.05	0.2	0.12	1.2	0.2	<0.05	13	1.2
L138W 10200 N	Soil			11	15	0.23	67	0.006	<1	1.83	0.005	0.06	0.1	0.07	0.8	0.4	0.06	7	2.0
L138W 10250 N	Soil			I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.
L138W 10300 N	Soil			52	17	0.25	167	0.011	2	4.48	0.010	0.06	0.2	0.51	2.8	0.2	0.24	5	2.4
L138W 10350 N	Soil			6	21	0.21	55	0.012	<1	1.90	0.005	0.05	0.1	0.09	2.2	0.2	<0.05	10	1.1
L138W 10400 N	Soil			7	15	0.21	52	0.006	1	1.90	0.005	0.05	0.2	0.13	1.7	0.2	<0.05	7	2.0
L138W 10450 N	Soil			13	16	0.36	144	0.006	1	1.38	0.006	0.08	0.1	0.03	1.8	0.2	<0.05	7	3.4
L138W 10500 N	Soil			9	18	0.32	110	0.006	2	1.43	0.006	0.07	0.2	0.07	2.1	0.2	<0.05	6	2.7
L138W 10550 N	Soil			4	5	0.03	74	0.006	1	0.28	0.009	0.01	<0.1	0.06	1.1	<0.1	0.75	<1	2.9
L138W 10600 N	Soil			6	9	0.10	73	0.004	<1	0.99	0.005	0.06	0.1	0.14	0.7	0.3	0.08	6	4.7

This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.



ACME ANALYTICAL LABORATORIES LTD.
1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**

110 - 325 Howe St.
Vancouver BC V6C 1Z7 Canada

Project: Zymo

Report Date: September 02, 2008

Page: 3 of 4 Part 1

CERTIFICATE OF ANALYSIS

SMI08000715.1

Method	Analyte	Unit	MDL	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
				Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	P
				ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	
				0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	0.001
L138W 10650 N	Soil			39.8	962.8	41.5	123	<0.1	25.7	16.9	967	4.72	41.9	1.1	30.1	1.6	28	0.2	2.2	0.8	61	0.12	0.055
L138W 10700 N	Soil			12.0	549.7	66.2	126	0.1	23.6	19.6	1979	5.42	53.1	2.1	31.1	1.5	14	0.4	2.8	1.3	56	0.04	0.071
L138W 10750 N	Soil			8.2	119.5	22.3	25	0.4	6.5	2.6	133	3.04	20.6	0.4	39.3	0.9	4	0.2	1.3	0.7	64	0.01	0.068
L138W 10800 N	Soil			11.9	676.1	69.4	180	0.2	30.9	21.8	1411	5.58	53.4	1.9	37.3	3.2	21	0.5	4.5	1.3	53	0.12	0.112
L138W 10850 N	Soil			12.9	741.3	58.7	142	0.7	19.8	14.7	1005	4.68	47.5	3.8	38.3	1.8	26	0.4	3.5	0.9	52	0.08	0.130
L138W 10900 N	Soil			29.8	2935	39.3	91	0.6	10.7	23.3	4116	4.93	2036	4.6	74.4	0.8	208	1.2	20.2	4.7	37	0.59	0.151
L138W 10950 N	Soil			17.9	135.8	17.0	35	0.1	3.2	22.3	4184	2.81	317.5	0.6	10.6	0.1	130	0.5	1.5	0.8	41	0.38	0.063
L138W 11000 N	Soil			2.9	62.4	36.0	51	0.7	4.9	3.4	202	3.45	28.3	1.1	8.0	0.6	9	0.1	0.9	0.4	54	0.08	0.122
L138W 11050 N	Soil			1.6	15.8	10.2	24	0.5	5.0	2.7	260	3.95	8.4	0.5	3.0	0.1	13	0.7	0.4	0.3	68	0.08	0.047
L138W 11100 N	Soil			0.7	6.4	15.7	32	0.1	7.5	4.9	847	1.40	4.8	0.3	2.3	0.3	17	<0.1	0.3	0.4	43	0.14	0.040
L138W 11150 N	Soil			1.5	18.2	15.3	26	<0.1	6.6	2.5	112	5.03	14.9	0.3	3.2	0.8	4	0.1	0.8	0.3	80	<0.01	0.028
L138W 11200 N	Soil			2.6	28.6	41.3	49	2.3	12.9	8.8	174	2.78	14.6	2.0	4.8	0.6	13	0.2	0.8	0.4	81	0.07	0.234
L146W 9000 N	Soil			2.4	80.5	72.6	128	0.5	9.5	5.0	291	3.86	49.0	2.0	11.3	0.2	19	0.2	2.7	0.9	64	0.10	0.069
L146W 9050 N	Soil			3.1	195.6	90.1	91	3.9	11.3	6.5	390	4.02	42.2	3.7	12.3	0.3	13	0.8	1.9	0.7	43	0.07	0.111
L146W 9100 N	Soil			5.1	81.6	73.4	142	1.1	12.2	7.3	326	5.81	89.9	1.4	26.0	0.6	9	1.2	2.8	1.3	68	0.04	0.087
L146W 9150 N	Soil			8.2	108.7	56.4	126	1.0	11.7	8.9	433	6.09	180.0	0.6	24.6	1.9	7	0.4	3.0	1.2	62	0.05	0.084
L146W 9200 N	Soil			2.7	47.1	24.8	87	0.3	4.9	4.0	207	3.50	53.3	0.4	36.8	0.4	5	0.2	2.1	1.1	71	0.02	0.076
L146W 9250 N	Soil			7.7	110.1	50.1	131	1.3	9.9	7.9	537	4.41	53.2	0.8	20.2	1.8	6	0.4	2.6	1.4	49	0.02	0.087
L146W 9300 N	Soil			3.2	115.6	98.8	232	0.8	16.8	11.6	1033	5.01	74.9	1.4	31.3	1.9	12	0.8	4.1	1.7	58	0.07	0.103
L146W 9350 N	Soil			12.5	44.7	83.5	88	0.4	6.4	4.0	279	4.50	52.4	2.6	15.6	0.4	8	0.5	1.9	1.3	62	0.05	0.133
L146W 9400 N	Soil			2.3	50.8	73.5	85	0.9	6.1	7.0	469	3.57	41.1	1.1	15.3	0.2	40	0.5	1.6	1.5	52	0.49	0.102
L146W 9450 N	Soil			3.7	59.5	62.4	142	0.3	10.3	6.7	568	3.99	95.1	0.8	7.5	0.4	19	0.4	2.9	1.2	78	0.23	0.046
L146W 9500 N	Soil			3.5	49.2	37.4	41	0.5	6.4	2.7	194	2.75	20.3	1.1	14.2	0.2	7	0.2	0.8	0.7	56	0.03	0.053
L146W 9550 N	Soil			2.3	67.3	73.1	200	0.7	12.7	11.3	1019	4.98	67.6	1.4	22.4	0.3	30	0.5	2.5	1.6	77	0.43	0.135
L146W 9600 N	Soil			4.0	90.2	169.3	254	0.9	15.3	20.8	1519	7.57	112.4	2.6	22.0	0.6	40	0.8	2.9	2.5	75	0.63	0.206
L146W 9650 N	Soil			2.0	55.2	85.9	236	0.6	17.2	12.4	1241	4.21	47.4	2.1	9.0	0.8	31	0.5	1.9	1.0	62	0.41	0.126
L146W 9700N	Soil			3.1	60.9	105.3	139	0.5	12.5	11.5	837	5.91	63.9	1.5	20.1	0.6	10	0.4	2.2	1.0	75	0.07	0.100
L146W 9750 N	Soil			1.4	21.9	22.4	32	<0.1	6.4	2.5	126	1.98	19.5	0.7	9.8	<0.1	9	<0.1	0.8	0.6	49	0.03	0.083
L146W 9800 N	Soil			4.1	32.4	39.1	31	0.7	4.1	2.0	170	2.94	23.9	0.8	8.4	0.4	5	0.1	0.9	0.6	60	0.01	0.062
L146W 9900 N	Soil			4.5	53.1	44.8	86	0.7	9.0	5.2	346	4.80	112.1	1.0	11.9	0.7	11	<0.1	1.9	0.9	68	0.07	0.076

This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.



AcmeLabs ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
Report Date: September 02, 2008

Page: 3 of 4 **Part** 2

CERTIFICATE OF ANALYSIS

SMI08000715.1

Method	Analyte	Unit	MDL	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15		
				La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
				ppm	ppm	%	ppm	%	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm		
				1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.05	0.5		
L138W 10650 N	Soil			10	24	0.45	116	0.004	2	1.89	0.006	0.09	<0.1	0.06	3.7	0.2	<0.05	6	2.9
L138W 10700 N	Soil			9	24	0.33	76	0.004	2	2.04	0.005	0.07	<0.1	0.16	3.6	0.3	<0.05	5	2.0
L138W 10750 N	Soil			4	13	0.13	40	0.002	<1	1.75	0.004	0.05	<0.1	0.09	1.6	0.3	<0.05	8	1.1
L138W 10800 N	Soil			11	20	0.35	119	0.007	2	1.73	0.006	0.10	<0.1	0.18	6.3	0.2	<0.05	4	2.4
L138W 10850 N	Soil			11	17	0.28	103	0.004	1	2.04	0.005	0.08	0.1	0.25	4.2	0.3	<0.05	5	1.8
L138W 10900 N	Soil			29	9	0.18	698	0.003	2	1.30	0.006	0.07	<0.1	0.23	4.6	0.6	<0.05	3	3.2
L138W 10950 N	Soil			5	6	0.12	709	0.004	<1	0.95	0.004	0.05	<0.1	0.04	0.7	0.3	<0.05	5	<0.5
L138W 11000 N	Soil			11	15	0.11	64	0.005	<1	2.46	0.005	0.04	<0.1	0.16	2.3	0.1	<0.05	7	1.0
L138W 11050 N	Soil			4	10	0.11	62	0.020	1	1.93	0.006	0.04	<0.1	0.06	1.7	0.1	<0.05	9	0.9
L138W 11100 N	Soil			4	14	0.20	134	0.006	1	1.32	0.005	0.04	<0.1	0.05	1.3	0.1	<0.05	8	<0.5
L138W 11150 N	Soil			3	17	0.09	30	0.013	1	1.47	0.003	0.02	0.1	0.07	1.8	0.1	<0.05	9	<0.5
L138W 11200 N	Soil			13	22	0.22	100	0.006	2	2.89	0.009	0.03	<0.1	0.30	2.3	0.4	<0.05	6	0.7
L146W 9000 N	Soil			8	12	0.11	107	0.007	2	1.12	0.004	0.04	0.1	0.10	1.2	0.2	<0.05	5	<0.5
L146W 9050 N	Soil			14	14	0.19	88	0.007	2	2.20	0.006	0.04	0.1	0.48	1.2	0.2	<0.05	4	1.0
L146W 9100 N	Soil			8	16	0.25	65	0.007	1	1.87	0.004	0.04	0.2	0.17	2.4	0.2	<0.05	7	1.1
L146W 9150 N	Soil			6	15	0.21	63	0.004	2	2.03	0.005	0.04	0.1	0.17	3.1	0.3	<0.05	6	1.4
L146W 9200 N	Soil			8	8	0.06	41	0.007	3	0.90	0.004	0.04	0.2	0.05	1.4	0.2	<0.05	7	<0.5
L146W 9250 N	Soil			6	15	0.20	60	0.003	<1	1.87	0.004	0.04	0.1	0.13	2.4	0.2	<0.05	5	1.4
L146W 9300 N	Soil			8	16	0.30	77	0.006	2	1.63	0.005	0.06	0.2	0.22	4.0	0.2	<0.05	4	1.3
L146W 9350 N	Soil			11	14	0.12	78	0.006	1	1.58	0.004	0.04	0.2	0.11	1.1	0.3	<0.05	6	<0.5
L146W 9400 N	Soil			15	9	0.09	190	0.006	2	1.04	0.005	0.04	0.2	0.11	1.0	0.2	<0.05	6	1.0
L146W 9450 N	Soil			8	14	0.15	190	0.009	<1	1.06	0.005	0.06	0.2	0.05	2.1	0.1	<0.05	6	0.8
L146W 9500 N	Soil			9	13	0.10	53	0.008	1	1.31	0.005	0.04	0.2	0.07	0.8	0.2	<0.05	7	0.5
L146W 9550 N	Soil			11	18	0.22	180	0.010	1	1.38	0.006	0.06	0.1	0.09	1.8	0.1	<0.05	7	0.7
L146W 9600 N	Soil			17	16	0.27	182	0.011	1	1.96	0.007	0.05	0.1	0.15	2.5	0.2	0.06	8	1.5
L146W 9650 N	Soil			20	19	0.33	143	0.007	2	1.97	0.007	0.06	0.1	0.17	3.6	0.2	<0.05	5	1.9
L146W 9700N	Soil			11	19	0.24	78	0.008	1	2.06	0.004	0.05	0.2	0.13	2.0	0.2	<0.05	8	1.5
L146W 9750 N	Soil			6	13	0.12	45	0.008	2	1.05	0.006	0.04	0.1	0.10	0.6	0.2	<0.05	10	<0.5
L146W 9800 N	Soil			7	12	0.08	33	0.008	<1	1.61	0.003	0.04	0.2	0.15	1.2	0.3	<0.05	8	0.8
L146W 9900 N	Soil			7	17	0.24	51	0.006	1	2.00	0.005	0.05	0.1	0.07	1.7	0.3	<0.05	8	1.3

This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
 Report Date: September 02, 2008

Page: 4 of 4 Part 1

CERTIFICATE OF ANALYSIS

SMI08000715.1

Method	Analyte	Unit	MDL	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15			
				Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	P	
				ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	%			
				0.1	0.1	0.1	1	0.1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	0.001
L146W	9950 N	Soil		10.4	101.9	57.8	85	0.9	11.0	6.9	560	7.40	43.1	1.4	22.7	1.2	7	0.6	1.8	1.0	77	0.04	0.132	
L146W	10000 N	Soil		6.6	94.2	78.6	112	0.8	15.4	12.4	537	9.20	58.8	1.3	22.8	1.6	8	0.4	3.2	1.9	71	0.02	0.109	
L146W	10050 N	Soil		8.2	96.7	56.1	88	0.3	10.4	6.5	300	4.81	39.1	1.0	18.8	1.6	8	0.1	1.9	1.0	57	0.04	0.094	
L146W	10100 N	Soil		5.3	48.6	48.7	81	0.4	12.3	7.0	499	6.28	47.1	0.9	106.3	0.2	8	0.3	1.7	0.8	100	0.03	0.188	
L146W	10150N	Soil		3.8	62.7	52.9	127	1.5	11.0	15.5	2322	5.28	63.4	1.2	12.7	0.2	18	0.3	2.7	1.3	83	0.17	0.117	
L146W	10200 N	Soil		3.7	60.5	58.7	66	0.3	11.7	6.0	274	7.47	51.9	0.7	9.9	0.6	6	0.2	2.7	0.8	78	0.03	0.091	
L146W	10250 N	Soil		6.9	85.5	51.6	79	0.3	7.8	7.4	406	6.17	52.3	1.0	15.3	0.6	6	0.4	2.2	1.1	80	0.02	0.107	
L146W	10300 N	Soil		3.0	32.0	27.5	41	3.5	8.6	4.1	219	5.33	22.1	0.7	4.8	0.3	8	0.2	1.2	0.6	80	0.03	0.275	
L146W	10350 N	Soil		16.1	348.7	79.0	331	1.3	28.6	23.6	1262	6.29	95.0	3.2	43.0	1.3	39	0.9	5.1	1.5	59	0.26	0.111	
L146W	10400 N	Soil		7.3	60.3	36.0	103	0.5	8.5	6.7	348	7.35	38.1	1.9	6.2	0.3	24	0.4	2.3	0.8	98	0.16	0.080	
L146W	10450 N	Soil		5.2	144.6	60.9	171	0.2	13.0	12.4	1107	4.08	26.1	7.8	8.2	0.6	21	1.0	1.8	1.0	52	0.16	0.103	
L146W	10500 N	Soil		3.5	37.0	29.6	44	1.0	4.3	3.0	252	4.81	34.0	0.7	12.7	1.1	6	<0.1	1.5	0.9	89	0.01	0.060	
L146W	10550 N	Soil		3.3	59.4	47.8	67	0.7	10.0	6.4	372	6.82	36.1	0.7	9.8	0.9	6	0.1	1.4	1.0	82	0.02	0.081	
L146W	10600 N	Soil		7.0	106.2	90.0	74	1.7	7.7	7.4	435	9.05	86.7	1.2	48.1	2.0	6	0.3	2.8	1.8	109	0.02	0.135	
L146W	10650 N	Soil		1.5	40.6	45.0	76	0.1	11.9	9.8	726	6.39	25.7	0.5	2.7	1.3	4	0.1	1.2	0.5	71	0.01	0.047	
L146W	10700 N	Soil		5.6	70.9	28.8	87	1.2	7.5	7.7	506	4.84	32.1	0.9	8.6	0.3	15	0.6	1.1	0.5	75	0.10	0.085	
L146W	10750 N	Soil		0.7	10.6	7.7	31	0.7	2.5	1.5	142	1.04	5.7	0.2	4.1	<0.1	17	<0.1	0.5	0.2	25	0.26	0.101	
L146W	10800 N	Soil		2.7	23.8	32.4	33	0.2	5.6	2.8	145	3.68	23.7	0.7	2.7	0.6	8	0.1	1.2	0.5	80	0.03	0.161	



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
 Report Date: September 02, 2008

Page: 4 of 4 Part 2

CERTIFICATE OF ANALYSIS

SMI08000715.1

Method	Analyte	Unit	MDL	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15		
				La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
				ppm	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm		
				1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.01	0.01	0.05	1	0.5		
L146W	9950 N	Soil		10	18	0.23	48	0.008	1	2.70	0.004	0.05	0.2	0.21	2.9	0.2	<0.05	9	2.3
L146W	10000 N	Soil		7	22	0.32	60	0.007	2	2.65	0.005	0.05	0.2	0.17	2.9	0.2	<0.05	7	2.9
L146W	10050 N	Soil		6	18	0.22	47	0.007	<1	2.52	0.008	0.04	0.2	0.19	2.2	0.2	<0.05	6	1.6
L146W	10100 N	Soil		6	19	0.23	50	0.014	2	1.68	0.005	0.05	0.2	0.23	1.4	0.2	<0.05	11	1.1
L146W	10150N	Soil		12	16	0.19	74	0.011	1	1.65	0.007	0.06	0.2	0.11	2.0	0.2	<0.05	8	1.9
L146W	10200 N	Soil		5	17	0.22	47	0.007	2	1.72	0.005	0.04	0.2	0.15	2.0	0.2	<0.05	8	1.8
L146W	10250 N	Soil		7	16	0.14	40	0.008	1	1.94	0.005	0.04	0.3	0.15	2.1	0.2	<0.05	8	1.4
L146W	10300 N	Soil		5	13	0.16	69	0.011	1	1.62	0.004	0.04	0.2	0.14	1.2	0.2	<0.05	8	0.9
L146W	10350 N	Soil		15	16	0.29	147	0.007	2	1.77	0.009	0.08	0.1	0.16	3.8	0.2	<0.05	5	3.3
L146W	10400 N	Soil		6	15	0.17	75	0.012	<1	1.57	0.009	0.04	0.2	0.06	1.8	0.1	<0.05	11	1.0
L146W	10450 N	Soil		11	16	0.23	164	0.007	<1	1.87	0.008	0.06	0.1	0.08	2.4	0.3	<0.05	7	1.4
L146W	10500 N	Soil		7	14	0.12	45	0.010	<1	1.83	0.005	0.04	0.2	0.11	2.1	0.3	<0.05	10	0.6
L146W	10550 N	Soil		6	18	0.21	40	0.008	1	1.99	0.006	0.04	0.1	0.13	2.4	0.2	<0.05	9	1.3
L146W	10600 N	Soil		6	17	0.17	44	0.012	1	1.98	0.003	0.05	0.2	0.33	3.2	0.3	<0.05	11	2.4
L146W	10650 N	Soil		4	22	0.35	44	0.005	1	2.57	0.005	0.03	<0.1	0.08	3.0	0.2	<0.05	8	0.7
L146W	10700 N	Soil		7	15	0.24	105	0.008	1	2.08	0.006	0.03	0.2	0.11	1.2	0.1	<0.05	9	0.9
L146W	10750 N	Soil		2	6	0.05	53	0.002	2	0.63	0.006	0.04	0.1	0.19	0.3	0.1	<0.05	4	0.7
L146W	10800 N	Soil		4	14	0.10	68	0.012	1	1.09	0.004	0.04	0.2	0.11	1.6	0.2	<0.05	8	0.7

QUALITY CONTROL REPORT

SMI08000715.1

Method	Analyte	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
		Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	P
Unit		ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	%	
MDL		0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	0.001
Pulp Duplicates																					
L138W 9050 N	Soil	1.4	52.9	58.8	154	0.8	17.7	10.0	2530	4.13	39.9	1.0	6.0	0.3	17	0.8	2.2	0.5	55	0.10	0.171
REP L138W 9050 N	QC	1.5	58.6	64.9	160	0.8	17.8	11.3	2696	4.42	42.8	1.0	8.3	0.3	18	0.9	2.8	0.6	60	0.11	0.178
L138W 9600 N	Soil	2.3	77.0	39.2	109	3.1	8.6	6.3	383	1.35	8.6	2.4	7.8	0.4	28	0.3	1.2	0.5	27	0.27	0.237
REP L138W 9600 N	QC	2.4	77.6	38.0	117	3.2	8.6	6.1	375	1.37	8.3	2.5	5.2	0.4	27	0.3	1.2	0.4	30	0.26	0.258
L138W 11050 N	Soil	1.6	15.8	10.2	24	0.5	5.0	2.7	260	3.95	8.4	0.5	3.0	0.1	13	0.7	0.4	0.3	68	0.08	0.047
REP L138W 11050 N	QC	1.1	17.3	10.3	25	0.5	4.7	2.7	257	3.96	8.1	0.5	1.7	0.1	13	0.7	0.4	0.3	68	0.08	0.045
L146W 9050 N	Soil	3.1	195.6	90.1	91	3.9	11.3	6.5	390	4.02	42.2	3.7	12.3	0.3	13	0.8	1.9	0.7	43	0.07	0.111
REP L146W 9050 N	QC	2.9	207.1	95.1	96	4.0	11.4	6.1	400	4.05	43.5	4.1	15.5	0.4	13	0.8	2.0	0.7	43	0.07	0.117
L146W 9950 N	Soil	10.4	101.9	57.8	85	0.9	11.0	6.9	560	7.40	43.1	1.4	22.7	1.2	7	0.6	1.8	1.0	77	0.04	0.132
REP L146W 9950 N	QC	10.9	109.4	60.7	91	0.9	11.8	7.6	583	7.57	44.6	1.4	26.1	0.9	8	0.6	2.1	1.1	82	0.04	0.139
Reference Materials																					
STD DS7	Standard	20.7	120.3	80.7	422	1.1	61.2	10.0	628	2.42	52.9	5.6	70.3	4.7	73	6.8	6.8	5.0	91	0.92	0.073
STD DS7	Standard	20.3	103.6	73.6	396	0.8	58.9	9.4	593	2.31	53.1	5.0	65.3	4.4	72	5.8	6.3	4.9	82	0.91	0.072
STD DS7	Standard	20.1	119.3	75.5	412	0.9	55.7	9.6	675	2.51	51.8	5.2	85.2	4.7	77	6.1	5.8	5.0	86	0.92	0.075
STD DS7	Standard	17.3	104.8	70.2	369	0.8	52.4	9.5	687	2.47	45.2	4.9	83.9	4.3	69	5.5	5.7	4.4	85	0.82	0.067
STD DS7 Expected		20.9	109	70.6	411	0.9	56	9.7	627	2.39	48.2	4.9	70	4.4	69	6.4	5.9	4.5	86	0.93	0.08
BLK	Blank	<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01	<0.001
BLK	Blank	<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01	<0.001
BLK	Blank	<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01	<0.001
BLK	Blank	<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01	<0.001

QUALITY CONTROL REPORT

SMI08000715.1

Method	Analyte	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
		La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
Unit		ppm	ppm	%	ppm	%	ppm	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
MDL		1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.05	1	0.5	
Pulp Duplicates																	
L138W 9050 N	Soil	14	15	0.18	215	0.009	3	1.60	0.006	0.06	0.1	0.34	5.3	0.2	0.05	5	0.8
REP L138W 9050 N	QC	15	16	0.19	230	0.013	5	1.64	0.006	0.07	0.2	0.21	6.2	0.2	0.08	5	<0.5
L138W 9600 N	Soil	38	17	0.22	130	0.006	2	2.18	0.007	0.05	<0.1	0.24	3.3	0.2	0.14	4	2.1
REP L138W 9600 N	QC	37	17	0.23	132	0.007	3	2.24	0.007	0.05	<0.1	0.22	3.6	0.2	0.16	5	2.1
L138W 11050 N	Soil	4	10	0.11	62	0.020	1	1.93	0.006	0.04	<0.1	0.06	1.7	0.1	<0.05	9	0.9
REP L138W 11050 N	QC	4	10	0.11	61	0.025	2	1.88	0.007	0.04	<0.1	0.07	1.8	0.1	<0.05	10	<0.5
L146W 9050 N	Soil	14	14	0.19	88	0.007	2	2.20	0.006	0.04	0.1	0.48	1.2	0.2	<0.05	4	1.0
REP L146W 9050 N	QC	15	15	0.19	94	0.009	3	2.25	0.006	0.04	0.2	0.50	1.5	0.2	<0.05	5	1.7
L146W 9950 N	Soil	10	18	0.23	48	0.008	1	2.70	0.004	0.05	0.2	0.21	2.9	0.2	<0.05	9	2.3
REP L146W 9950 N	QC	11	18	0.25	51	0.014	3	2.81	0.005	0.06	0.2	0.23	3.0	0.3	<0.05	10	2.8
Reference Materials																	
STD DS7	Standard	13	177	1.06	381	0.128	40	0.98	0.079	0.46	4.1	0.22	2.6	4.6	0.19	5	4.3
STD DS7	Standard	12	166	1.00	355	0.109	39	0.90	0.076	0.42	4.1	0.17	2.4	4.3	0.18	4	2.8
STD DS7	Standard	13	162	1.10	414	0.135	38	1.05	0.084	0.54	3.9	0.21	2.6	4.4	0.18	5	3.5
STD DS7	Standard	11	154	1.14	403	0.136	34	1.09	0.084	0.56	3.6	0.17	2.6	4.1	0.16	5	3.5
STD DS7 Expected		13	163	1.05	370	0.124	39	0.959	0.073	0.44	3.8	0.2	2.5	4.2	0.21	5	3.5
BLK	Blank	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
BLK	Blank	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
BLK	Blank	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
BLK	Blank	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.

Vancouver BC V6C 1Z7 Canada

Submitted By:

Glen Garratt

Receiving Lab:

Canada-Smithers

Received:

August 11, 2008

Report Date:

September 02, 2008

Page:

1 of 5

CERTIFICATE OF ANALYSIS

SMI08000726.1

CLIENT JOB INFORMATION

Project: Zymo
Shipment ID: zy-so-08-06
P.O. Number
Number of Samples: 120

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
DISP-RJT-SOIL Immediate Disposal of Soil Reject

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Mincord Exploration Consultants Ltd.
110 - 325 Howe St.
Vancouver BC V6C 1Z7
Canada

CC: Bob Johnston

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status
SS80	120	Dry at 60C sieve 100g to -80 mesh		
Dry at 60C	120	Dry at 60C		
1DX15	113	1:1:1 Aqua Regia digestion ICP-MS analysis	15	Completed

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only. All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.



AcmeLabs ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
Report Date: September 02, 2008

Page: 2 of 5 **Part** 1

CERTIFICATE OF ANALYSIS

SMI08000726.1

Method	Analyte	Unit	MDL	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15			
				Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	P	
				ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	%		
				0.1	0.1	0.1	1	0.1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	0.001
L92W	105 00 N	Soil		7.7	22.4	11.5	48	0.2	6.5	2.9	141	2.67	42.0	0.5	5.8	0.4	7	0.2	2.2	0.3	94	<0.01	0.029	
L92W	105 50 N	Soil		3.4	71.4	45.4	105	2.4	11.5	7.2	784	4.21	30.9	2.1	17.2	0.4	19	0.3	1.5	0.6	56	0.23	0.165	
L92W	106 00 N	Soil		3.6	80.4	42.2	82	1.6	19.0	8.4	381	7.45	81.7	1.1	19.8	0.6	8	0.5	5.0	0.6	96	0.02	0.083	
L92W	106 50 N	Soil		2.0	61.6	22.7	34	0.7	7.7	2.8	138	2.53	27.0	1.1	4.3	0.1	8	0.2	1.4	0.5	58	0.02	0.083	
L92W	107 00 N	Soil		2.4	40.8	38.0	88	0.5	18.9	8.7	612	5.68	42.9	0.9	4.9	0.8	10	0.3	2.9	0.4	91	0.03	0.119	
L92W	107 50 N	Soil		2.9	55.8	95.3	102	0.6	13.5	8.3	681	5.33	43.7	1.5	5.7	0.3	11	0.6	2.7	0.5	76	0.04	0.130	
L92W	108 00 N	Soil		1.7	102.4	37.5	58	1.0	12.7	4.8	258	3.71	19.9	1.4	4.2	0.1	10	0.5	1.6	0.4	83	0.03	0.099	
L92W	108 50 N	Soil		I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	
L92W	109 00 N	Soil		3.4	301.2	38.1	60	0.3	11.1	5.6	286	4.49	19.6	4.0	32.9	0.2	10	0.2	1.4	1.2	62	0.06	0.062	
L92W	109 50 N	Soil		1.9	356.9	27.6	40	2.2	10.5	3.3	143	1.60	11.0	4.8	11.6	<0.1	18	0.1	1.1	0.3	34	0.12	0.159	
L92W	110 00 N	Soil		4.9	333.9	73.6	115	0.6	12.6	7.6	454	5.28	33.2	1.4	36.1	2.0	10	0.2	3.2	0.6	81	0.04	0.088	
L92W	111 00 N	Soil		5.7	463.1	34.0	117	0.6	6.3	9.2	403	4.54	48.2	2.1	80.2	0.2	67	0.4	3.7	1.6	83	0.36	0.090	
L92W	111 50 N	Soil		I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	
L92W	112 00 N	Soil		6.6	80.6	18.4	43	0.6	3.9	2.4	162	2.94	61.8	0.8	28.5	1.0	21	<0.1	8.6	0.7	96	<0.01	0.046	
L92W	112 50 N	Soil		9.1	350.3	30.5	91	1.0	4.6	6.7	488	6.39	82.4	6.7	61.3	1.1	27	0.2	27.8	1.4	62	0.11	0.203	
L92W	113 00 N	Soil		3.0	206.2	40.2	103	1.0	12.9	6.9	425	5.05	44.3	2.5	12.7	0.2	23	0.2	5.1	0.7	81	0.12	0.084	
L92W	113 50 N	Soil		5.4	78.7	26.7	19	0.7	2.7	1.6	79	3.12	73.7	1.4	59.4	0.3	15	<0.1	4.7	1.0	89	0.09	0.063	
L92W	114 00 N	Soil		1.5	332.7	33.9	19	6.5	2.4	43.5	3039	22.61	17.4	15.3	19.7	4.2	39	0.2	3.8	0.2	17	0.27	0.256	
L92W	114 50 N	Soil		5.6	392.7	83.7	35	0.8	3.8	82.0	3504	21.19	126.5	19.6	23.2	6.3	21	0.3	15.8	0.4	35	0.16	0.183	
L92W	115 00 N	Soil		I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	
L92W	117 00 N	Soil		2.3	92.2	221.5	145	1.9	7.8	6.9	735	6.79	29.7	3.1	11.9	2.8	28	0.4	2.2	2.6	111	0.14	0.065	
L92W	117 50 N	Soil		1.3	59.9	64.9	185	1.0	18.6	12.7	1127	4.73	30.0	1.2	11.2	1.5	18	0.4	2.3	0.7	87	0.14	0.167	
L92W	118 00 N	Soil		1.9	76.4	65.5	121	1.6	14.3	7.2	355	7.39	27.2	0.8	3.9	2.5	10	0.2	1.7	0.5	92	0.03	0.120	
L92W	118 50 N	Soil		4.2	336.5	405.8	199	2.2	10.4	16.9	3027	6.93	106.3	2.9	63.3	7.3	9	0.5	3.6	2.3	68	0.06	0.202	
L92W	119 00 N	Soil		4.6	136.9	939.9	189	7.9	8.4	11.6	3921	7.10	219.4	2.2	44.9	2.3	11	0.5	11.9	8.6	83	0.08	0.354	
L92W	119 50 N	Soil		7.2	33.8	15.0	4571	1.0	10.3	56.2	>10000	16.98	73.1	28.1	3.3	0.2	338	2.8	2.2	0.1	4	0.08	0.452	
L92W	120 00 N	Soil		3.0	28.9	77.2	77	0.4	3.8	6.2	1875	4.70	29.8	1.1	6.0	1.0	8	<0.1	2.0	2.6	54	0.02	0.201	
L94W	105 00 N	Soil		2.0	37.3	36.5	59	1.1	11.2	5.4	611	5.05	43.3	0.6	2.1	0.1	10	0.3	1.7	0.7	109	0.02	0.214	
L94W	105 50 N	Soil		2.2	246.9	35.7	90	0.5	13.0	7.4	432	5.40	51.1	2.5	5.7	0.4	30	0.4	3.0	0.7	109	0.06	0.096	
L94W	106 00 N	Soil		3.8	150.8	40.1	79	2.1	12.6	6.9	434	7.42	61.2	2.1	10.1	0.5	9	0.5	3.6	0.6	86	0.03	0.089	

This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.



AcmeLabs ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
Report Date: September 02, 2008

Page: 2 of 5 **Part** 2

CERTIFICATE OF ANALYSIS

SMI08000726.1

Method	Analyte	Unit	MDL	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
				La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
				ppm	ppm	%	ppm	%	ppm	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
				1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.05	1	0.5	
L92W	105 00 N	Soil		5	16	0.04	42	0.010	2	0.68	0.002	0.03	0.1	0.03	1.2	0.1	<0.05	7	<0.5
L92W	105 50 N	Soil		14	22	0.24	141	0.007	1	2.47	0.007	0.05	0.1	0.21	1.6	0.3	0.06	7	1.0
L92W	106 00 N	Soil		5	31	0.32	48	0.016	2	1.79	0.004	0.05	0.2	0.12	2.9	0.2	<0.05	9	1.3
L92W	106 50 N	Soil		9	18	0.13	34	0.010	1	1.63	0.003	0.05	0.1	0.12	0.9	0.3	<0.05	8	0.6
L92W	107 00 N	Soil		5	30	0.37	64	0.010	2	2.26	0.005	0.06	0.2	0.11	3.0	0.2	<0.05	8	0.9
L92W	107 50 N	Soil		8	23	0.26	54	0.016	2	2.11	0.005	0.05	0.2	0.16	1.8	0.2	<0.05	8	1.0
L92W	108 00 N	Soil		8	24	0.20	46	0.010	2	1.75	0.004	0.06	0.1	0.15	1.1	0.6	<0.05	10	0.8
L92W	108 50 N	Soil		I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.
L92W	109 00 N	Soil		12	20	0.20	45	0.012	1	1.53	0.005	0.06	0.2	0.09	1.1	0.5	<0.05	8	1.8
L92W	109 50 N	Soil		12	17	0.18	32	0.004	2	1.91	0.014	0.04	<0.1	0.23	0.3	0.2	0.16	4	2.2
L92W	110 00 N	Soil		7	21	0.29	56	0.007	3	2.84	0.005	0.07	0.2	0.15	3.1	0.4	<0.05	8	1.2
L92W	111 00 N	Soil		15	10	0.08	117	0.008	<1	1.06	0.005	0.06	0.2	0.04	0.8	0.3	<0.05	6	1.3
L92W	111 50 N	Soil		I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.
L92W	112 00 N	Soil		8	9	0.03	37	0.012	2	0.62	0.003	0.04	0.7	0.03	0.8	0.2	<0.05	8	0.6
L92W	112 50 N	Soil		12	7	0.05	63	0.004	2	1.30	0.004	0.07	2.3	0.17	2.2	0.4	<0.05	5	2.3
L92W	113 00 N	Soil		7	18	0.18	61	0.011	3	1.31	0.006	0.08	0.2	0.12	1.4	0.3	<0.05	7	1.5
L92W	113 50 N	Soil		7	8	0.10	41	0.004	<1	1.13	0.003	0.04	0.2	0.05	0.8	0.2	<0.05	7	0.8
L92W	114 00 N	Soil		17	7	0.05	145	0.011	1	2.70	0.007	0.02	0.1	0.57	3.5	0.1	0.12	1	2.8
L92W	114 50 N	Soil		44	17	0.02	59	0.010	<1	4.87	0.004	<0.01	0.2	0.33	9.7	0.1	0.09	1	6.1
L92W	115 00 N	Soil		I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.
L92W	117 00 N	Soil		17	19	0.15	49	0.025	2	1.64	0.005	0.05	0.2	0.11	2.5	0.2	<0.05	13	0.9
L92W	117 50 N	Soil		7	23	0.40	108	0.014	3	2.57	0.006	0.09	0.2	0.25	4.1	0.2	<0.05	8	0.6
L92W	118 00 N	Soil		5	31	0.30	59	0.013	2	3.62	0.005	0.04	0.1	0.30	3.7	0.1	<0.05	8	1.0
L92W	118 50 N	Soil		10	23	0.23	57	0.008	2	5.20	0.005	0.06	0.2	0.36	3.5	0.4	<0.05	6	4.1
L92W	119 00 N	Soil		11	20	0.20	57	0.012	3	2.40	0.005	0.06	0.2	0.23	2.3	0.5	<0.05	10	3.2
L92W	119 50 N	Soil		2	2	<0.01	441	0.009	<1	0.24	0.003	0.13	<0.1	0.21	0.8	0.5	<0.05	8	1.4
L92W	120 00 N	Soil		13	7	0.06	67	0.006	2	1.22	0.003	0.04	0.1	0.06	0.9	0.6	<0.05	6	1.3
L94W	105 00 N	Soil		4	21	0.23	51	0.015	2	1.82	0.005	0.06	0.2	0.13	1.5	0.2	<0.05	11	0.6
L94W	105 50 N	Soil		29	23	0.33	70	0.024	4	2.15	0.006	0.07	0.3	0.09	3.0	0.5	0.07	10	2.2
L94W	106 00 N	Soil		11	23	0.22	43	0.013	2	1.74	0.004	0.05	0.2	0.25	1.9	0.3	0.06	10	2.2

This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**

110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo

Report Date: September 02, 2008

Page: 3 of 5 Part 1

CERTIFICATE OF ANALYSIS

SMI08000726.1

Method	Analyte	Unit	MDL	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
				Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	P
				ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	%		
				0.1	0.1	0.1	1	0.1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	2	0.01	0.001
L94W	106 50 N	Soil		3.3	332.1	34.8	65	2.0	7.3	4.1	228	6.34	111.5	5.8	7.2	0.4	13	0.4	3.4	0.4	68	0.02	0.131
L94W	107 00 N	Soil		2.7	102.8	19.1	99	0.9	16.6	9.4	570	4.05	65.7	0.9	10.7	0.8	14	0.7	3.3	0.3	58	0.11	0.226
L94W	107 50 N	Soil		1.8	191.7	40.4	48	4.3	4.3	2.3	144	2.29	17.6	5.1	8.1	0.2	8	0.2	1.2	0.5	57	0.03	0.130
L94W	108 00 N	Soil		5.2	95.2	50.1	65	2.4	3.5	2.9	1638	2.78	34.1	1.2	28.7	0.1	9	0.4	1.3	0.7	55	0.02	0.129
L94W	108 50 N	Soil		12.3	1361	569.0	265	2.6	6.6	52.7	5455	5.73	175.4	6.1	401.0	2.7	18	0.8	12.0	1.6	41	0.09	0.213
L94W	109 00 N	Soil		20.1	3688	288.0	619	1.5	24.8	71.3	>10000	9.39	1116	14.4	51.0	2.5	148	11.1	2.8	0.8	17	0.91	0.200
L94W	109 50 N	Soil		I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.
L94W	110 00 N	Soil		3.3	598.9	63.8	79	0.5	5.1	29.0	8880	9.93	32.4	13.9	15.1	0.9	46	0.3	2.2	0.4	32	0.25	0.130
L94W	111 00 N	Soil		I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.
L94W	111 50 N	Soil		3.8	246.6	39.3	15	0.9	2.4	0.8	55	1.17	12.9	3.2	24.2	0.3	14	0.1	2.0	0.8	34	0.03	0.074
L94W	112 00 N	Soil		6.3	378.7	63.6	23	1.5	4.5	1.7	102	7.98	54.8	8.2	32.0	0.6	15	0.1	5.7	0.5	67	0.03	0.182
L94W	112 50 N	Soil		5.6	201.4	38.6	57	0.6	4.6	3.5	200	6.41	38.0	3.7	39.8	0.5	17	0.2	6.4	1.1	68	0.02	0.135
L94W	113 00 N	Soil		2.0	672.1	19.2	6	2.8	1.9	0.4	33	5.44	106.3	141.8	6.0	0.3	9	0.1	3.0	<0.1	11	0.05	0.865
L94W	113 50 N	Soil		3.1	174.7	54.2	76	0.8	9.5	6.4	451	6.48	42.2	2.5	23.4	1.9	20	0.3	5.0	1.1	81	0.05	0.190
L94W	114 00 N	Soil		8.8	105.3	44.3	24	2.5	2.2	1.4	88	2.05	15.9	1.6	25.4	0.1	17	<0.1	1.7	1.8	55	0.02	0.073
L94W	114 50 N	Soil		11.1	165.1	32.7	43	3.1	3.1	2.0	125	6.46	66.7	11.6	22.2	0.2	13	<0.1	3.6	2.7	125	0.04	0.171
L94W	115 00 N	Soil		3.6	346.8	89.5	9	10.0	1.2	2.5	488	8.33	12.9	66.7	19.3	1.2	6	<0.1	0.4	0.2	6	0.03	0.361
L94W	115 50 N	Soil		I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.
L94W	116 00 N	Soil		0.8	9.0	6.4	22	0.7	2.9	1.5	105	1.18	5.0	0.5	5.2	0.4	7	<0.1	1.0	0.2	41	<0.01	0.019
L94W	116 50 N	Soil		7.9	144.7	85.3	100	1.5	3.9	4.5	370	8.94	48.2	1.3	50.0	1.9	8	0.2	3.5	3.6	89	0.02	0.211
L94W	117 00 N	Soil		16.8	2662	275.9	377	4.7	18.7	60.5	>10000	6.75	54.3	15.3	85.9	3.7	13	16.1	3.7	3.6	75	0.07	0.311
L94W	117 50 N	Soil		3.0	34.2	38.8	44	3.1	5.0	3.0	178	4.07	29.1	0.6	8.6	0.7	10	<0.1	2.2	1.2	111	0.01	0.053
L94W	118 00 N	Soil		7.8	76.0	551.4	47	5.5	3.9	2.6	543	10.36	59.6	1.5	84.5	3.2	48	0.2	11.6	13.1	59	0.02	0.279
L94W	118 50 N	Soil		3.8	55.3	40.2	98	0.3	4.7	3.5	234	3.32	43.8	1.0	9.4	0.8	10	0.2	2.7	1.6	117	0.01	0.031
L94W	119 00 N	Soil		4.4	1987	126.7	397	3.5	15.5	67.7	>10000	1.54	14.1	35.6	48.1	4.5	61	8.3	1.2	0.3	9	0.27	0.331
L94W	119 50 N	Soil		2.5	217.4	39.3	50	1.8	3.4	3.0	153	2.56	13.6	3.7	19.0	0.3	30	0.2	1.3	0.7	80	0.08	0.029
L94W	120 00 N	Soil		2.3	1675	76.6	697	1.6	18.7	42.3	>10000	3.45	112.1	51.0	9.2	1.4	148	14.0	2.3	0.5	6	0.65	0.302
L94W	120 50 N	Soil		1.7	45.3	75.4	283	0.3	5.4	37.4	2953	5.98	45.5	1.9	7.4	1.8	95	0.1	0.8	3.1	62	0.40	0.067
L94W	121 00 N	Soil		1.2	41.7	36.4	271	0.4	16.5	11.7	893	4.05	22.9	1.7	6.9	1.0	73	0.2	2.2	0.9	79	0.35	0.088
L94W	121 50 N	Soil		1.0	35.4	13.9	91	0.2	7.8	8.8	475	5.44	15.9	0.4	1.9	0.8	15	0.1	1.1	0.3	83	0.14	0.144



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
 Report Date: September 02, 2008

Page: 3 of 5 Part 2

CERTIFICATE OF ANALYSIS

SMI08000726.1

Method	Analyte	Unit	MDL	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
				La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
				ppm	ppm	%	ppm	%	ppm	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
				1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.01	0.01	0.01	0.05	1	0.05	
L94W	106 50 N	Soil		23	18	0.12	93	0.010	2	1.79	0.006	0.06	0.2	0.43	1.5	0.5	0.08	7	3.2
L94W	107 00 N	Soil		6	19	0.26	80	0.013	2	2.56	0.006	0.04	0.2	0.20	2.5	0.3	<0.05	4	0.8
L94W	107 50 N	Soil		15	11	0.10	40	0.005	1	1.61	0.004	0.05	0.1	0.30	1.4	0.5	<0.05	7	1.1
L94W	108 00 N	Soil		7	11	0.07	45	0.006	2	1.30	0.004	0.06	0.1	0.18	0.6	0.6	<0.05	6	0.8
L94W	108 50 N	Soil		23	10	0.13	62	0.007	2	3.13	0.005	0.06	0.2	0.34	3.6	0.7	0.08	5	5.0
L94W	109 00 N	Soil		49	9	0.10	169	0.006	2	4.49	0.007	0.04	1.5	0.22	8.6	0.7	0.24	3	5.2
L94W	109 50 N	Soil		I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.
L94W	110 00 N	Soil		20	11	0.15	52	0.006	2	2.00	0.007	0.06	0.2	0.14	2.9	0.5	0.15	3	2.2
L94W	111 00 N	Soil		I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.
L94W	111 50 N	Soil		11	9	0.05	55	0.003	1	1.30	0.005	0.07	0.2	0.21	0.6	0.4	0.08	6	0.7
L94W	112 00 N	Soil		14	9	0.14	71	0.011	3	1.78	0.010	0.08	0.3	0.13	1.7	0.3	0.12	4	2.5
L94W	112 50 N	Soil		12	10	0.14	58	0.007	2	1.34	0.009	0.08	0.3	0.10	1.2	0.4	<0.05	6	1.1
L94W	113 00 N	Soil		13	8	0.01	49	0.006	2	1.24	0.013	0.02	<0.1	0.21	5.6	<0.1	0.18	1	8.0
L94W	113 50 N	Soil		8	18	0.30	73	0.012	2	1.92	0.005	0.10	0.2	0.10	3.1	0.4	<0.05	9	1.6
L94W	114 00 N	Soil		11	6	0.04	76	0.007	2	0.67	0.005	0.06	0.2	0.19	0.5	0.3	<0.05	4	<0.5
L94W	114 50 N	Soil		10	9	0.08	34	0.013	2	0.87	0.004	0.06	0.2	0.34	1.2	0.2	0.10	7	1.4
L94W	115 00 N	Soil		15	7	0.02	17	0.005	2	1.48	0.004	0.03	0.1	0.57	2.0	<0.1	0.19	2	2.3
L94W	115 50 N	Soil		I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.
L94W	116 00 N	Soil		5	7	0.03	29	0.010	5	0.55	0.003	0.05	0.1	0.04	1.0	0.2	<0.05	6	<0.5
L94W	116 50 N	Soil		6	10	0.10	55	0.010	2	1.40	0.004	0.05	0.3	0.16	2.2	0.3	<0.05	9	1.5
L94W	117 00 N	Soil		10	20	0.25	179	0.015	3	3.03	0.005	0.08	0.2	0.19	3.8	0.6	0.10	12	2.6
L94W	117 50 N	Soil		6	13	0.10	46	0.014	2	1.40	0.004	0.05	0.1	0.09	2.2	0.2	<0.05	13	0.5
L94W	118 00 N	Soil		16	11	0.10	286	0.009	2	1.34	0.024	0.13	0.3	0.21	1.4	0.5	0.29	8	3.3
L94W	118 50 N	Soil		13	12	0.06	46	0.025	2	0.79	0.003	0.05	0.2	0.04	1.8	0.2	<0.05	7	<0.5
L94W	119 00 N	Soil		70	9	0.04	55	0.015	2	9.98	0.006	0.01	0.1	0.49	13.2	0.4	0.21	7	4.3
L94W	119 50 N	Soil		37	10	0.04	38	0.013	3	1.01	0.004	0.06	0.1	0.07	1.2	0.2	<0.05	6	0.9
L94W	120 00 N	Soil		360	6	0.04	107	0.008	3	6.81	0.012	0.02	0.3	0.19	4.8	0.3	0.30	6	9.4
L94W	120 50 N	Soil		9	11	0.15	61	0.004	2	1.68	0.007	0.05	0.1	0.05	2.4	0.3	0.05	5	3.3
L94W	121 00 N	Soil		10	20	0.42	145	0.018	3	1.80	0.014	0.09	0.1	0.11	5.0	0.2	<0.05	6	<0.5
L94W	121 50 N	Soil		5	11	0.12	78	0.002	3	2.56	0.005	0.06	<0.1	0.39	6.2	0.3	<0.05	6	<0.5

This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project:

Zymo

Report Date:

September 02, 2008

Page:

4 of 5

Part 1

CERTIFICATE OF ANALYSIS

SMI08000726.1

Method Analyte	Unit	MDL	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
			Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	P
			ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%
L94W	122 00 N	Soil	2.0	21.1	22.1	49	<0.1	6.2	3.8	266	3.40	22.1	0.7	2.6	0.3	11	0.3	0.9	0.7	79	0.03	0.055
L94W	122 50 N	Soil	1.5	32.9	35.4	75	0.1	12.9	9.0	970	7.74	26.5	1.0	1.2	0.6	15	0.3	1.4	0.3	115	0.07	0.220
L94W	123 00 N	Soil	1.8	25.5	35.5	90	0.2	9.6	10.4	2080	4.46	19.6	1.3	1.6	0.2	51	0.4	1.0	0.4	86	0.18	0.151
L94W	123 50 N	Soil	1.1	20.8	16.9	51	0.2	11.4	4.1	177	3.02	13.6	0.5	2.8	0.4	19	0.2	0.8	0.3	58	0.08	0.076
L96W	105 00 N	Soil	2.1	67.5	69.8	81	0.4	14.6	7.0	482	6.17	59.8	1.7	7.5	1.5	8	0.4	3.7	0.9	82	0.02	0.085
L96W	105 50 N	Soil	1.9	24.0	24.8	52	0.5	7.4	3.5	325	4.76	45.9	0.5	5.0	0.7	8	<0.1	2.7	0.7	90	0.01	0.088
L96W	106 00 N	Soil	2.1	29.3	22.9	40	0.3	8.6	4.4	424	6.03	33.0	0.6	1.6	0.6	10	0.2	2.0	0.4	77	0.02	0.216
L96W	106 50 N	Soil	1.5	23.7	25.6	60	0.4	5.0	2.9	248	3.14	37.0	0.6	5.9	0.1	10	0.2	2.0	1.1	80	0.02	0.073
L96W	107 00 N	Soil	3.4	50.0	77.5	104	0.8	7.4	3.6	241	7.32	57.8	1.2	10.4	1.2	12	0.4	2.9	1.4	105	0.04	0.335
L96W	107 50 N	Soil	3.4	53.6	113.7	113	2.9	6.9	24.5	2820	5.45	45.2	3.1	7.2	0.3	16	1.7	1.8	0.5	60	0.08	0.130
L96W	108 00 N	Soil	3.0	69.2	81.4	83	0.2	6.7	3.5	302	4.93	70.1	1.7	17.2	0.3	17	0.2	2.9	3.3	82	0.08	0.118
L96W	108 50 N	Soil	6.8	263.5	106.7	86	0.8	9.8	160.5	8355	3.94	138.1	4.2	21.7	0.4	14	1.0	3.4	0.7	38	0.09	0.227
L96W	109 00 N	Soil	6.4	57.3	50.7	67	0.3	5.4	3.0	259	5.04	57.7	1.1	19.9	0.3	18	0.1	2.3	1.4	57	0.03	0.216
L96W	109 50 N	Soil	5.7	129.9	53.2	81	0.7	6.5	5.4	300	5.70	36.7	1.1	31.9	1.5	15	0.2	3.7	0.9	59	0.04	0.136
L96W	110 00 N	Soil	6.5	177.9	90.8	170	0.9	7.4	5.5	349	5.51	43.7	2.5	35.7	0.9	17	0.5	3.7	2.9	59	0.04	0.107
L96W	110 50 N	Soil	6.7	82.3	46.1	103	2.0	2.8	4.0	465	3.57	25.4	1.0	24.0	0.8	6	0.5	2.2	1.2	69	0.02	0.096
L96W	111 00 N	Soil	7.4	142.5	60.4	81	0.4	4.5	3.2	227	3.86	47.8	1.5	27.5	0.3	29	0.3	7.0	1.3	77	0.06	0.055
L96W	111 50 N	Soil	4.3	65.3	31.1	48	1.2	3.1	2.2	140	2.07	19.9	1.5	21.6	0.6	15	0.1	1.6	1.0	44	0.04	0.078
L96W	112 00 N	Soil	5.7	92.0	40.8	88	0.5	3.6	3.0	214	5.55	39.9	0.7	19.2	1.5	5	0.1	3.2	1.5	70	0.01	0.095
L96W	112 50 N	Soil	8.3	337.5	102.5	184	0.4	9.3	10.3	731	7.03	56.7	2.9	72.6	4.1	12	0.3	6.1	2.0	54	0.04	0.135
L96W	113 00 N	Soil	2.4	27.6	4.0	32	0.1	13.7	3.7	79	1.60	10.7	0.5	22.4	1.8	3	<0.1	0.8	0.3	44	<0.01	0.020
L96W	113 50 N	Soil	2.9	213.4	56.4	88	0.4	10.0	4.5	258	5.70	45.8	1.1	35.9	4.3	11	<0.1	5.0	2.8	59	<0.01	0.053
L96W	114 00 N	Soil	3.1	107.3	21.8	107	0.5	20.3	11.7	2131	3.53	20.0	2.0	12.7	0.4	19	0.3	2.0	0.9	45	0.11	0.078
L144W	90 00 N	Soil	3.9	73.9	44.9	147	0.8	9.0	4.8	271	3.78	56.8	1.3	18.1	0.3	9	0.2	2.8	0.8	49	0.05	0.075
L144W	90 50 N	Soil	5.0	81.7	64.7	125	1.4	10.0	8.3	564	5.74	56.6	1.5	29.4	0.6	9	0.3	2.7	0.9	50	0.06	0.115
L144W	91 00 N	Soil	5.2	90.4	42.5	181	0.2	12.8	10.0	544	4.40	59.2	1.0	12.4	0.9	23	0.4	2.9	1.1	61	0.26	0.090
L144W	91 50 N	Soil	6.3	81.8	32.5	89	0.2	8.2	6.7	302	3.85	40.2	0.5	23.6	0.4	8	0.5	2.2	0.8	72	0.05	0.052
L144W	92 00 N	Soil	3.1	90.4	85.3	192	0.5	10.1	7.8	529	5.28	88.6	0.9	16.3	0.5	9	0.7	4.6	1.8	75	0.07	0.073
L144W	92 50 N	Soil	2.6	61.3	76.3	171	0.3	11.8	12.1	1815	6.16	93.1	0.8	17.9	0.4	8	0.6	3.6	1.7	78	0.04	0.140
L144W	93 00 N	Soil	2.2	20.7	22.4	47	0.2	3.6	5.2	1030	5.83	26.7	0.4	13.4	0.2	4	0.6	1.6	0.7	72	0.02	0.115

This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.



AcmeLabs ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
Report Date: September 02, 2008

Page: 4 of 5 **Part** 2

CERTIFICATE OF ANALYSIS

SMI08000726.1

Method	Analyte	Unit	MDL	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
				La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
				ppm	ppm	%	ppm	%	ppm	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
				1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.01	0.01	0.01	0.05	1	0.5	
L94W	122 00 N	Soil		7	15	0.14	74	0.014	2	1.52	0.006	0.06	0.1	0.06	1.9	0.3	<0.05	10	<0.5
L94W	122 50 N	Soil		5	28	0.30	109	0.030	3	2.51	0.006	0.06	0.1	0.14	3.5	0.1	<0.05	12	0.7
L94W	123 00 N	Soil		10	19	0.20	207	0.013	3	1.99	0.006	0.09	0.1	0.08	1.8	0.2	0.05	10	<0.5
L94W	123 50 N	Soil		5	19	0.23	72	0.008	2	1.83	0.005	0.05	<0.1	0.13	2.1	0.1	<0.05	7	<0.5
L96W	105 00 N	Soil		5	24	0.31	50	0.006	2	2.24	0.004	0.05	0.2	0.18	2.6	0.2	<0.05	8	1.1
L96W	105 50 N	Soil		5	17	0.11	39	0.011	<1	1.49	0.004	0.04	0.1	0.06	2.2	0.2	<0.05	10	<0.5
L96W	106 00 N	Soil		4	18	0.15	50	0.017	1	1.28	0.004	0.03	0.2	0.14	1.5	0.1	<0.05	8	<0.5
L96W	106 50 N	Soil		5	11	0.08	61	0.009	<1	0.88	0.003	0.05	0.1	0.05	0.9	0.2	<0.05	9	<0.5
L96W	107 00 N	Soil		6	21	0.18	52	0.013	<1	1.80	0.003	0.05	0.2	0.15	2.5	0.2	<0.05	10	1.1
L96W	107 50 N	Soil		14	18	0.10	131	0.007	<1	2.06	0.005	0.04	0.2	0.26	1.4	0.2	<0.05	7	2.0
L96W	108 00 N	Soil		10	13	0.12	121	0.014	<1	0.83	0.005	0.08	0.2	0.04	1.0	0.2	<0.05	7	<0.5
L96W	108 50 N	Soil		16	11	0.18	90	0.007	2	2.08	0.009	0.07	0.1	0.24	1.8	1.1	0.05	4	2.2
L96W	109 00 N	Soil		8	11	0.06	57	0.008	2	0.98	0.003	0.05	0.2	0.15	0.9	0.3	<0.05	6	1.2
L96W	109 50 N	Soil		7	12	0.14	68	0.004	1	1.34	0.004	0.06	0.1	0.14	1.8	0.3	<0.05	5	1.4
L96W	110 00 N	Soil		9	12	0.17	121	0.004	<1	1.71	0.004	0.07	0.2	0.12	1.8	0.3	<0.05	5	1.6
L96W	110 50 N	Soil		7	6	0.06	68	0.005	<1	1.28	0.003	0.06	0.2	0.08	1.3	0.4	<0.05	6	<0.5
L96W	111 00 N	Soil		11	11	0.11	129	0.009	<1	1.12	0.004	0.10	0.2	0.04	1.1	0.3	<0.05	7	0.7
L96W	111 50 N	Soil		9	7	0.12	80	0.003	<1	1.34	0.004	0.07	0.1	0.10	0.8	0.3	<0.05	5	<0.5
L96W	112 00 N	Soil		7	12	0.06	31	0.009	2	1.11	0.003	0.05	0.1	0.05	1.6	0.3	<0.05	7	0.9
L96W	112 50 N	Soil		12	12	0.16	90	0.004	1	1.72	0.005	0.07	0.2	0.15	4.2	0.4	<0.05	4	2.7
L96W	113 00 N	Soil		11	5	0.02	21	0.005	2	0.41	0.001	0.03	0.1	0.03	0.9	0.2	<0.05	4	<0.5
L96W	113 50 N	Soil		7	17	0.16	56	0.005	2	1.99	0.004	0.07	0.2	0.09	2.3	0.3	<0.05	7	1.8
L96W	114 00 N	Soil		8	19	0.24	144	0.007	1	1.56	0.006	0.05	0.2	0.07	1.3	0.2	<0.05	7	1.4
L144W	90 00 N	Soil		8	9	0.12	43	0.005	<1	1.28	0.007	0.07	0.1	0.11	1.4	0.2	<0.05	6	0.9
L144W	90 50 N	Soil		8	13	0.20	47	0.007	1	1.84	0.007	0.03	0.1	0.33	2.2	0.3	0.08	5	1.7
L144W	91 00 N	Soil		11	13	0.25	241	0.004	1	1.70	0.007	0.06	0.1	0.08	3.9	0.2	<0.05	6	0.7
L144W	91 50 N	Soil		7	11	0.14	89	0.007	2	1.00	0.005	0.05	0.1	0.06	1.8	0.2	<0.05	6	0.8
L144W	92 00 N	Soil		16	13	0.17	78	0.007	1	1.53	0.005	0.05	0.1	0.10	2.5	0.2	<0.05	7	0.8
L144W	92 50 N	Soil		8	17	0.22	82	0.010	2	1.68	0.005	0.05	0.2	0.11	2.0	0.2	<0.05	8	0.9
L144W	93 00 N	Soil		6	9	0.13	41	0.006	2	1.47	0.003	0.03	0.2	0.11	1.3	0.2	<0.05	9	0.7

This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

ACME ANALYTICAL LABORATORIES LTD.

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project:

Zymo

Report Date:

September 02, 2008

Page:

5 of 5

Part 1

CERTIFICATE OF ANALYSIS

SMI08000726.1

Method	Analyte	Unit	MDL	1DX15 Mo ppm	1DX15 Cu ppm	1DX15 Pb ppm	1DX15 Zn ppm	1DX15 Ag ppm	1DX15 Ni ppm	1DX15 Co ppm	1DX15 Mn ppm	1DX15 Fe %	1DX15 As ppm	1DX15 U ppm	1DX15 Au ppb	1DX15 Th ppm	1DX15 Sr ppm	1DX15 Cd ppm	1DX15 Sb ppm	1DX15 Bi ppm	1DX15 V ppm	1DX15 Ca %	1DX15 P %
				0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	0.001
L144W 93 50 N	Soil			2.4	40.2	66.2	121	0.4	5.6	11.1	6376	4.59	57.7	0.8	17.4	0.3	7	0.5	2.5	1.7	64	0.03	0.186
L144W 94 00 N	Soil			3.5	51.9	72.2	87	1.2	5.3	9.8	749	5.49	65.9	0.9	23.2	0.3	9	0.8	2.9	2.0	77	0.07	0.117
L144W 94 50 N	Soil			2.5	136.5	56.4	109	6.5	10.5	9.8	604	3.06	31.7	3.4	28.4	0.3	10	0.5	1.4	1.2	42	0.06	0.145
L144W 95 00 N	Soil			2.0	276.3	54.9	65	3.5	7.7	3.8	180	3.04	23.4	10.4	8.4	0.2	10	0.4	1.6	0.4	59	0.04	0.108
L144W 95 50 N	Soil			6.5	137.1	73.1	173	0.6	15.3	12.5	793	5.28	50.9	0.9	19.2	1.6	9	0.8	2.1	1.1	61	0.06	0.126
L144W 96 00 N	Soil			1.5	37.0	32.5	98	0.9	11.9	5.1	453	2.75	25.2	1.2	5.1	0.2	20	0.2	1.0	0.6	57	0.08	0.113
L144W 96 50 N	Soil			5.1	28.8	62.2	135	0.4	10.6	39.6	2173	6.50	186.2	0.9	10.0	1.0	15	0.7	1.4	0.3	58	0.10	0.112
L144W 97 00 N	Soil			2.2	41.9	37.9	134	0.5	17.8	36.0	2697	3.39	41.0	1.3	6.0	0.3	18	0.4	1.3	0.6	64	0.07	0.107
L144W 97 50 N	Soil			2.3	50.7	76.8	104	0.2	13.3	6.4	357	5.35	42.8	1.1	8.8	0.8	9	0.3	2.0	0.6	85	0.02	0.080
L144W 98 00 N	Soil			9.7	311.2	63.3	80	2.9	12.1	6.4	275	5.16	47.8	3.5	23.4	0.6	7	0.2	1.8	0.5	45	0.03	0.136
L144W 98 50 N	Soil			3.4	31.4	41.4	57	1.1	7.5	3.7	174	2.55	26.8	0.8	8.2	0.1	12	0.2	0.8	0.7	60	0.05	0.068
L144W 99 00 N	Soil			2.8	47.1	34.6	63	0.5	12.5	5.5	265	4.98	21.5	1.2	4.2	0.4	10	0.3	1.4	0.3	88	0.04	0.072
L144W 99 50 N	Soil			9.2	63.2	41.0	65	0.7	6.8	5.6	563	7.26	49.6	0.8	36.9	0.5	6	0.5	1.4	0.8	88	0.02	0.126
L144W 100 00 N	Soil			13.4	97.5	74.4	96	0.8	9.4	7.1	412	8.30	65.8	1.2	33.0	0.7	8	0.5	2.3	1.6	85	0.05	0.184
L144W 100 50 N	Soil			I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.
L144W 101 00 N	Soil			4.7	64.6	50.2	163	0.5	17.4	16.8	2418	4.96	32.0	1.0	10.4	0.3	34	0.4	1.9	0.6	73	0.17	0.190
L144W 101 50 N	Soil			2.0	20.2	21.8	24	0.2	3.3	2.5	1065	1.87	19.4	0.4	8.6	<0.1	7	<0.1	0.6	0.7	47	0.01	0.065
L144W 102 00 N	Soil			3.5	31.3	31.3	29	0.2	4.0	3.2	368	3.94	31.1	0.6	37.0	0.2	7	0.2	1.1	1.4	66	0.01	0.136
L144W 102 50 N	Soil			6.8	65.6	74.4	149	0.6	11.0	6.0	340	7.99	72.0	1.0	9.3	0.2	36	0.4	2.4	0.9	93	0.30	0.107
L144W 103 00 N	Soil			5.9	59.4	56.5	95	0.1	7.8	5.2	329	7.29	48.5	0.9	13.7	0.4	7	0.2	2.6	1.2	85	0.01	0.077
L144W 103 50 N	Soil			7.8	111.5	100.3	89	0.7	7.7	13.5	936	6.41	71.3	1.4	23.2	0.5	20	0.3	3.4	1.4	71	0.11	0.151
L144W 104 00 N	Soil			21.0	188.6	41.4	65	0.7	7.2	26.5	830	5.79	58.7	1.5	25.1	0.4	11	0.6	4.2	0.9	55	0.04	0.141
L144W 104 50 N	Soil			2.0	281.1	25.1	11	0.8	4.6	1.3	27	0.28	3.8	5.3	20.1	0.7	94	<0.1	0.3	0.6	15	0.24	0.238
L144W 105 00 N	Soil			4.8	149.0	37.9	178	0.5	15.0	13.5	553	5.74	73.8	2.1	30.3	0.6	22	0.3	2.0	1.2	67	0.12	0.153
L144W 105 50 N	Soil			3.8	74.4	35.0	103	0.6	14.6	18.1	1236	6.39	64.0	1.0	67.7	0.3	6	0.8	2.0	2.7	68	0.04	0.241
L144W 106 00 N	Soil			4.3	122.3	91.5	87	0.4	7.3	5.6	276	4.79	37.4	1.1	14.5	0.6	12	0.5	2.1	1.0	70	0.05	0.097
L144W 106 50 N	Soil			4.6	122.0	63.2	358	0.4	12.7	8.7	718	4.93	60.5	1.3	22.9	1.1	23	0.5	1.3	1.0	61	0.20	0.163
L144W 107 00 N	Soil			8.1	210.9	41.4	72	0.5	6.1	3.9	219	4.90	39.9	1.1	19.7	0.5	6	0.5	2.2	0.7	61	0.03	0.183
L144W 108 00 N	Soil			9.5	63.1	36.9	178	<0.1	14.0	14.4	764	3.71	21.1	0.9	3.7	0.8	10	0.4	0.9	0.5	67	0.04	0.094
L144W 108 50 N	Soil			7.6	44.0	18.7	58	1.0	6.6	2.9	135	3.67	42.4	0.5	14.4	1.1	21	0.2	0.8	0.5	72	0.13	0.074



AcmeLabs ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
Report Date: September 02, 2008

Page: 5 of 5 **Part** 2

CERTIFICATE OF ANALYSIS

SMI08000726.1

Method	Analyte	Unit	MDL	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15		
				La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
				ppm	ppm	%	ppm	%	ppm	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
				1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.01	0.01	0.01	0.05	1	0.5	
L144W 93 50 N	Soil			10	10	0.08	112	0.006	<1	1.18	0.004	0.04	0.2	0.09	1.0	0.4	<0.05	6	1.0
L144W 94 00 N	Soil			8	11	0.12	63	0.010	1	1.39	0.004	0.04	0.2	0.14	1.2	0.2	<0.05	8	1.0
L144W 94 50 N	Soil			13	15	0.23	60	0.007	2	2.44	0.006	0.05	0.1	0.74	1.1	0.2	0.06	6	1.9
L144W 95 00 N	Soil			53	17	0.15	70	0.017	3	1.97	0.011	0.06	0.2	0.32	3.1	0.4	<0.05	7	2.1
L144W 95 50 N	Soil			7	17	0.29	71	0.005	2	2.22	0.006	0.06	0.1	0.15	3.4	0.2	<0.05	5	1.8
L144W 96 00 N	Soil			8	16	0.26	77	0.008	2	1.62	0.006	0.06	0.1	0.11	1.1	0.2	<0.05	6	0.8
L144W 96 50 N	Soil			9	11	0.26	142	0.004	2	1.40	0.009	0.05	<0.1	0.06	2.6	0.3	<0.05	4	0.9
L144W 97 00 N	Soil			7	25	0.42	98	0.007	3	2.01	0.006	0.08	0.1	0.10	1.6	0.2	0.07	6	0.8
L144W 97 50 N	Soil			7	22	0.28	54	0.011	2	2.18	0.004	0.05	0.1	0.13	2.7	0.2	<0.05	8	1.2
L144W 98 00 N	Soil			15	16	0.25	47	0.008	1	2.71	0.007	0.06	0.2	0.38	1.7	0.2	0.07	8	3.1
L144W 98 50 N	Soil			8	14	0.18	66	0.007	1	1.44	0.005	0.07	0.1	0.07	0.8	0.2	<0.05	7	<0.5
L144W 99 00 N	Soil			7	20	0.27	60	0.016	2	1.98	0.005	0.05	0.1	0.13	2.6	0.2	<0.05	9	1.0
L144W 99 50 N	Soil			6	15	0.22	51	0.014	2	1.91	0.004	0.04	0.2	0.16	2.0	0.3	<0.05	11	1.4
L144W 100 00 N	Soil			6	17	0.29	39	0.011	1	2.01	0.005	0.05	0.1	0.16	2.3	0.2	0.06	8	2.3
L144W 100 50 N	Soil			I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.
L144W 101 00 N	Soil			9	20	0.30	123	0.009	1	2.18	0.007	0.07	0.1	0.07	1.8	0.3	0.07	8	1.7
L144W 101 50 N	Soil			7	9	0.10	43	0.012	2	1.22	0.004	0.05	<0.1	0.06	0.5	0.3	<0.05	9	0.6
L144W 102 00 N	Soil			6	12	0.11	34	0.006	1	1.62	0.005	0.04	<0.1	0.07	0.5	0.2	<0.05	8	0.9
L144W 102 50 N	Soil			8	18	0.23	107	0.015	2	1.90	0.008	0.05	0.2	0.10	1.6	0.1	<0.05	9	2.9
L144W 103 00 N	Soil			7	17	0.19	34	0.016	2	2.01	0.004	0.05	0.2	0.11	1.9	0.2	0.05	9	1.8
L144W 103 50 N	Soil			13	14	0.19	50	0.016	2	1.67	0.006	0.05	0.1	0.12	2.0	0.3	<0.05	7	2.5
L144W 104 00 N	Soil			15	10	0.19	46	0.007	2	1.55	0.005	0.06	0.1	0.12	1.2	0.3	0.06	6	3.5
L144W 104 50 N	Soil			19	10	0.11	137	0.004	2	1.59	0.013	0.03	<0.1	0.26	1.5	0.4	0.56	4	2.2
L144W 105 00 N	Soil			15	18	0.29	82	0.007	2	2.33	0.007	0.06	0.1	0.18	3.1	0.3	0.06	7	3.0
L144W 105 50 N	Soil			13	22	0.14	46	0.015	2	2.11	0.005	0.06	0.2	0.11	2.1	0.3	<0.05	8	1.1
L144W 106 00 N	Soil			10	14	0.15	56	0.006	2	1.88	0.004	0.07	0.1	0.11	1.7	0.3	<0.05	7	1.1
L144W 106 50 N	Soil			11	15	0.22	138	0.005	1	2.17	0.006	0.05	<0.1	0.07	2.8	0.2	<0.05	7	2.2
L144W 107 00 N	Soil			6	14	0.13	37	0.007	2	1.76	0.004	0.05	0.1	0.18	1.6	0.2	<0.05	7	1.7
L144W 108 00 N	Soil			7	17	0.25	112	0.005	1	2.40	0.007	0.06	0.4	0.07	2.5	0.2	<0.05	8	0.5
L144W 108 50 N	Soil			7	10	0.23	92	0.003	2	1.71	0.008	0.06	<0.1	0.09	2.6	0.3	<0.05	8	0.7

This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.

QUALITY CONTROL REPORT

SMI08000726.1

Method	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
Analyte	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	P	
Unit	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	%	
MDL	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	0.001	
Pulp Duplicates																					
L92W 113 50 N	Soil	5.4	78.7	26.7	19	0.7	2.7	1.6	79	3.12	73.7	1.4	59.4	0.3	15	<0.1	4.7	1.0	89	0.09	0.063
REP L92W 113 50 N	QC	5.3	80.2	28.1	20	0.7	3.1	1.9	85	3.28	78.8	1.6	45.9	0.3	17	<0.1	4.8	1.0	96	0.09	0.068
L94W 106 50 N	Soil	3.3	332.1	34.8	65	2.0	7.3	4.1	228	6.34	111.5	5.8	7.2	0.4	13	0.4	3.4	0.4	68	0.02	0.131
REP L94W 106 50 N	QC	3.3	354.3	36.5	62	2.0	7.5	4.1	238	6.63	114.0	6.0	8.4	0.3	15	0.3	3.5	0.3	69	0.03	0.138
L94W 116 00 N	Soil	0.8	9.0	6.4	22	0.7	2.9	1.5	105	1.18	5.0	0.5	5.2	0.4	7	<0.1	1.0	0.2	41	<0.01	0.019
REP L94W 116 00 N	QC	0.8	8.6	5.9	19	0.7	2.4	1.4	100	1.14	4.7	0.5	6.9	0.4	7	<0.1	0.9	0.2	42	<0.01	0.019
L96W 114 00 N	Soil	3.1	107.3	21.8	107	0.5	20.3	11.7	2131	3.53	20.0	2.0	12.7	0.4	19	0.3	2.0	0.9	45	0.11	0.078
REP L96W 114 00 N	QC	3.2	105.4	22.0	107	0.5	19.0	10.8	2145	3.44	19.4	2.0	18.8	0.3	20	0.3	1.8	0.9	46	0.10	0.075
L144W 99 00 N	Soil	2.8	47.1	34.6	63	0.5	12.5	5.5	265	4.98	21.5	1.2	4.2	0.4	10	0.3	1.4	0.3	88	0.04	0.072
REP L144W 99 00 N	QC	2.6	47.5	34.1	61	0.5	12.1	5.7	264	4.95	21.1	1.1	3.2	0.5	10	0.2	1.4	0.2	84	0.04	0.070
L144W 99 50 N	Soil	9.2	63.2	41.0	65	0.7	6.8	5.6	563	7.26	49.6	0.8	36.9	0.5	6	0.5	1.4	0.8	88	0.02	0.126
REP L144W 99 50 N	QC	8.8	63.6	39.8	63	0.7	6.6	5.6	555	7.14	47.8	0.9	23.9	0.5	7	0.5	1.5	0.8	88	0.02	0.122
Reference Materials																					
STD DS7	Standard	22.5	126.7	75.4	435	0.9	65.1	10.6	690	2.64	56.4	5.3	74.7	4.6	79	6.9	6.7	4.8	93	0.99	0.089
STD DS7	Standard	19.8	115.9	66.9	400	0.8	57.6	9.4	641	2.36	49.1	4.7	71.4	4.0	72	6.4	6.1	4.3	91	0.91	0.084
STD DS7	Standard	20.9	122.7	70.4	421	0.9	61.5	10.3	667	2.52	51.0	4.9	66.7	4.2	76	6.2	6.2	4.4	96	0.94	0.085
STD DS7	Standard	20.2	108.2	72.7	397	0.9	53.4	9.6	653	2.44	56.4	5.4	64.5	4.6	77	6.8	6.5	5.0	89	0.97	0.075
STD DS7	Standard	18.6	94.9	69.7	379	0.9	50.0	8.3	588	2.28	52.2	4.9	69.9	4.3	74	6.3	6.4	4.8	75	0.89	0.076
STD DS7	Standard	18.0	106.2	73.0	392	0.8	52.8	9.6	638	2.40	51.3	5.4	70.3	4.4	76	6.0	6.4	4.9	83	0.89	0.074
STD DS7 Expected		20.9	109	70.6	411	0.9	56	9.7	627	2.39	48.2	4.9	70	4.4	69	6.4	5.9	4.5	86	0.93	0.08
BLK	Blank	<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01	<0.001
BLK	Blank	<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01	<0.001
BLK	Blank	<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01	<0.001
BLK	Blank	<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	5	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01	<0.001
BLK	Blank	<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01	<0.001
BLK	Blank	<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01	<0.001

QUALITY CONTROL REPORT

SMI08000726.1

Method Analyte Unit MDL	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
	La ppm	Cr ppm	Mg %	Ba ppm	Ti %	B ppm	Al %	Na %	K %	W ppm	Hg ppm	Sc ppm	Tl ppm	S %	Ga ppm	Se ppm	
	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5	
Pulp Duplicates																	
L92W 113 50 N	Soil	7	8	0.10	41	0.004	<1	1.13	0.003	0.04	0.2	0.05	0.8	0.2	<0.05	7	0.8
REP L92W 113 50 N	QC	7	9	0.11	45	0.007	2	1.30	0.005	0.06	0.2	0.06	1.0	0.3	<0.05	8	0.8
L94W 106 50 N	Soil	23	18	0.12	93	0.010	2	1.79	0.006	0.06	0.2	0.43	1.5	0.5	0.08	7	3.2
REP L94W 106 50 N	QC	23	18	0.14	102	0.016	3	1.93	0.007	0.08	0.3	0.45	2.0	0.5	0.09	8	3.8
L94W 116 00 N	Soil	5	7	0.03	29	0.010	5	0.55	0.003	0.05	0.1	0.04	1.0	0.2	<0.05	6	<0.5
REP L94W 116 00 N	QC	5	7	0.03	27	0.006	3	0.54	0.003	0.04	<0.1	0.03	0.8	0.2	<0.05	6	<0.5
L96W 114 00 N	Soil	8	19	0.24	144	0.007	1	1.56	0.006	0.05	0.2	0.07	1.3	0.2	<0.05	7	1.4
REP L96W 114 00 N	QC	8	15	0.24	145	0.009	1	1.59	0.006	0.06	0.1	0.09	1.2	0.2	<0.05	7	1.8
L144W 99 00 N	Soil	7	20	0.27	60	0.016	2	1.98	0.005	0.05	0.1	0.13	2.6	0.2	<0.05	9	1.0
REP L144W 99 00 N	QC	7	20	0.27	58	0.010	1	1.92	0.005	0.05	0.1	0.12	2.6	0.2	<0.05	9	0.7
L144W 99 50 N	Soil	6	15	0.22	51	0.014	2	1.91	0.004	0.04	0.2	0.16	2.0	0.3	<0.05	11	1.4
REP L144W 99 50 N	QC	6	15	0.23	50	0.015	2	1.88	0.004	0.04	0.2	0.17	2.0	0.3	<0.05	11	1.4
Reference Materials																	
STD DS7	Standard	13	183	1.16	401	0.135	43	1.09	0.088	0.51	4.2	0.21	2.5	4.6	0.22	5	3.8
STD DS7	Standard	14	161	1.05	394	0.135	38	1.01	0.089	0.43	3.8	0.20	2.5	4.2	0.22	5	3.6
STD DS7	Standard	13	169	1.09	405	0.146	38	1.09	0.087	0.46	4.1	0.18	2.6	4.3	0.22	5	3.2
STD DS7	Standard	14	165	1.07	400	0.130	39	1.05	0.090	0.48	4.0	0.20	3.0	4.2	0.22	5	4.0
STD DS7	Standard	12	146	0.97	376	0.106	38	0.91	0.081	0.46	4.4	0.18	2.1	4.2	0.18	5	3.7
STD DS7	Standard	12	155	1.07	385	0.124	38	0.99	0.081	0.48	3.7	0.20	2.5	4.2	0.17	5	3.3
STD DS7 Expected		13	163	1.05	370	0.124	39	0.959	0.073	0.44	3.8	0.2	2.5	4.2	0.21	5	3.5
BLK	Blank	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
BLK	Blank	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
BLK	Blank	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
BLK	Blank	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
BLK	Blank	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
BLK	Blank	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.

Vancouver BC V6C 1Z7 Canada

Submitted By:

Glen Garratt

Receiving Lab:

Canada-Smithers

Received:

August 12, 2008

Report Date:

September 02, 2008

Page:

1 of 5

CERTIFICATE OF ANALYSIS

SMI08000740.1

CLIENT JOB INFORMATION

Project: Zymo
Shipment ID: zy-so-08-15
P.O. Number
Number of Samples: 115

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
DISP-RJT-SOIL Immediate Disposal of Soil Reject

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Mincord Exploration Consultants Ltd.
110 - 325 Howe St.
Vancouver BC V6C 1Z7
Canada

CC: Bob Johnston

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status
SS80	115	Dry at 60C sieve 100g to -80 mesh		
Dry at 60C	115	Dry at 60C		
1DX15	112	1:1:1 Aqua Regia digestion ICP-MS analysis	15	Completed

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only. All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

ACME ANALYTICAL LABORATORIES LTD.

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.
Vancouver BC V6C 1Z7 Canada

Project:

Zymo

Report Date:

September 02, 2008

Page:

2 of 5

Part 1

CERTIFICATE OF ANALYSIS

SMI08000740.1

Method	Analyte	Unit	MDL	1DX15 Mo ppm	1DX15 Cu ppm	1DX15 Pb ppm	1DX15 Zn ppm	1DX15 Ag ppm	1DX15 Ni ppm	1DX15 Co ppm	1DX15 Mn ppm	1DX15 Fe %	1DX15 As ppm	1DX15 U ppm	1DX15 Au ppb	1DX15 Th ppm	1DX15 Sr ppm	1DX15 Cd ppm	1DX15 Sb ppm	1DX15 Bi ppm	1DX15 V ppm	1DX15 Ca %	1DX15 P %
				0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	0.001
L102W 80 50N	Soil			1.0	22.4	35.1	130	1.0	6.2	2.3	193	2.28	23.8	1.5	8.8	0.4	18	0.4	0.8	0.5	40	0.07	0.068
L102W 81 00N	Soil			2.1	37.8	104.8	210	1.1	12.3	5.8	298	5.68	62.7	1.0	13.6	3.1	7	0.5	2.1	0.8	56	0.01	0.063
L102W 81 50N	Soil			1.5	51.2	104.7	305	0.5	22.9	13.0	1496	3.94	54.1	1.3	12.9	2.2	30	1.1	2.9	0.6	55	0.27	0.073
L102W 82 00N	Soil			1.0	15.4	15.2	47	1.0	2.8	1.8	125	1.40	13.2	0.4	172.8	0.8	5	<0.1	0.7	0.3	42	0.02	0.022
L102W 82 50N	Soil			1.6	33.5	158.5	211	2.1	8.9	4.4	345	5.46	66.9	1.0	8.1	1.8	47	0.3	2.6	1.5	60	0.52	0.096
L102W 83 50N	Soil			2.4	72.1	250.2	485	1.1	36.4	24.4	8641	4.38	100.6	4.4	38.1	1.7	38	3.3	2.9	1.3	46	0.49	0.101
L102W 84 00N	Soil			3.6	50.1	59.5	157	1.7	7.0	3.7	175	3.01	33.1	1.1	4.8	1.6	7	0.5	1.7	0.4	72	<0.01	0.030
L102W 84 50N	Soil			1.8	49.4	110.5	312	1.5	13.6	11.1	3225	4.56	78.8	1.3	14.8	1.3	11	0.7	2.2	0.9	63	0.03	0.130
L102W 85 00N	Soil			1.6	47.0	78.9	215	0.6	11.7	7.5	861	4.34	41.6	1.3	591.1	1.8	11	0.8	2.0	0.6	70	0.02	0.159
L102W 85 50N	Soil			1.6	45.3	153.2	446	0.6	18.6	16.9	2595	5.63	93.6	1.4	21.4	1.4	15	1.9	2.6	0.7	72	0.07	0.360
L102W 86 00N	Soil			1.4	34.2	68.0	292	1.1	13.8	7.4	871	4.04	46.5	1.0	32.2	1.3	13	0.8	1.6	0.7	73	0.03	0.094
L102W 86 50N	Soil			1.4	42.2	86.4	223	0.5	10.6	7.9	1520	3.83	42.4	1.0	9.1	0.5	14	0.5	1.6	0.9	65	0.03	0.110
L102W 87 00N	Soil			2.3	100.1	241.8	362	0.6	14.9	12.6	1572	7.28	115.0	1.6	35.5	1.2	12	0.3	3.2	4.7	81	0.05	0.621
L102W 87 50N	Soil			1.6	70.1	203.8	465	0.9	13.8	8.1	2048	4.83	64.2	1.5	9.6	0.6	15	1.2	2.0	2.1	65	0.06	0.101
L102W 88 00N	Soil			2.2	59.5	99.6	214	1.0	8.9	4.7	502	3.64	69.9	0.8	22.4	0.3	14	0.4	2.2	2.5	71	0.06	0.091
L102W 89 00N	Soil			1.7	57.3	118.9	271	1.9	16.0	11.6	1796	4.67	47.4	1.8	30.5	1.3	31	0.8	2.2	1.0	64	0.49	0.110
L102W 89 50N	Soil			1.9	76.4	206.6	255	2.1	13.7	8.2	877	5.54	80.8	2.8	24.2	2.1	12	0.5	2.0	1.7	65	0.10	0.163
L102W 90 00N	Soil			1.6	52.8	195.5	373	4.3	12.4	10.6	1998	5.08	72.3	1.4	27.8	0.6	21	1.1	1.6	2.0	64	0.26	0.196
L102W 90 50N	Soil			1.9	67.9	290.9	348	1.3	15.2	11.7	2006	6.11	110.2	1.7	26.8	1.0	21	1.2	2.0	3.5	66	0.15	0.373
L102W 91 00N	Soil			1.9	61.5	121.7	192	1.0	8.7	5.5	778	3.92	59.0	1.0	11.6	0.3	18	1.0	1.8	2.0	71	0.14	0.059
L102W 91 50N	Soil			2.4	103.7	251.8	342	0.8	13.3	13.3	2392	6.00	97.9	1.6	60.7	1.6	9	0.2	2.9	3.8	48	0.05	0.152
L102W 92 00N	Soil			3.3	63.6	125.5	212	0.5	8.3	3.0	349	3.61	83.1	1.2	26.9	0.3	7	<0.1	2.4	2.4	45	0.05	0.063
L102W 92 50N	Soil			2.5	52.5	208.2	320	1.9	12.1	22.8	4566	6.37	116.0	1.6	27.1	2.2	14	1.1	2.7	4.1	51	0.13	0.067
L102W 93 00N	Soil			2.5	95.2	77.4	301	1.2	15.9	4.7	564	4.13	78.7	1.0	25.8	0.5	58	0.9	2.3	4.0	80	0.61	0.072
L102W 93 50N	Soil			2.3	84.4	177.4	385	0.9	25.0	19.7	5211	5.50	158.0	2.3	36.9	0.5	62	2.1	2.1	6.6	43	0.64	0.159
L102W 94 00N	Soil			1.7	89.7	190.7	390	1.5	13.2	14.5	2659	5.47	77.2	2.2	18.1	0.6	21	1.3	2.3	3.7	56	0.17	0.127
L102W 94 50N	Soil			2.3	80.7	92.9	178	1.8	10.4	5.3	542	3.64	41.6	1.4	20.3	0.4	11	0.5	2.3	1.9	66	0.04	0.084
L102W 95 00N	Soil			2.5	143.4	165.5	423	2.3	34.8	11.6	2673	4.32	59.4	2.6	30.8	0.9	30	2.7	3.2	2.5	48	0.24	0.150
L102W 95 50N	Soil			3.0	82.5	146.6	237	0.8	7.9	4.5	596	5.94	75.8	1.2	15.7	1.8	8	0.3	3.1	5.1	70	0.02	0.198
L102W 96 00N	Soil			2.5	72.1	120.4	152	0.7	9.4	8.1	916	5.53	57.0	1.0	14.4	1.5	10	0.3	3.0	2.4	53	0.04	0.236



AcmeLabs ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
Report Date: September 02, 2008

Page: 2 of 5 **Part** 2

CERTIFICATE OF ANALYSIS

SMI08000740.1

Method	Analyte	Unit	MDL	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15		
				La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
				ppm	ppm	%	ppm	%	ppm	%	%	ppm	ppm	ppm	ppm	ppm	ppm		
				1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.05	0.5		
L102W 80 50N	Soil			11	11	0.08	158	0.004	<1	1.23	0.005	0.05	0.1	0.13	1.2	0.2	<0.05	4	<0.5
L102W 81 00N	Soil			8	19	0.13	75	0.005	<1	1.91	0.004	0.04	0.2	0.17	2.8	0.3	<0.05	6	<0.5
L102W 81 50N	Soil			10	12	0.22	182	0.023	2	0.60	0.009	0.07	0.1	0.08	4.5	0.1	0.16	2	<0.5
L102W 82 00N	Soil			11	6	0.02	26	0.006	5	0.49	0.001	0.04	<0.1	0.07	0.8	0.3	<0.05	4	<0.5
L102W 82 50N	Soil			6	12	0.13	79	0.004	2	1.08	0.004	0.04	0.1	0.14	2.5	0.2	<0.05	5	0.5
L102W 83 50N	Soil			16	13	0.17	293	0.007	3	0.81	0.005	0.08	0.1	0.18	4.7	0.3	0.08	2	1.5
L102W 84 00N	Soil			9	9	0.03	97	0.007	3	0.89	0.002	0.05	0.1	0.06	1.9	0.2	<0.05	4	<0.5
L102W 84 50N	Soil			8	16	0.11	160	0.005	2	1.66	0.003	0.06	0.1	0.14	2.6	0.3	<0.05	4	0.9
L102W 85 00N	Soil			9	18	0.10	142	0.007	2	1.77	0.004	0.04	0.1	0.14	3.2	0.2	<0.05	5	<0.5
L102W 85 50N	Soil			7	19	0.18	142	0.009	2	1.97	0.005	0.06	0.1	0.12	3.3	0.2	<0.05	5	0.8
L102W 86 00N	Soil			9	19	0.17	150	0.009	3	1.98	0.005	0.06	0.1	0.18	3.0	0.2	<0.05	5	<0.5
L102W 86 50N	Soil			8	16	0.13	127	0.007	2	1.29	0.005	0.05	<0.1	0.09	1.8	0.3	<0.05	5	0.6
L102W 87 00N	Soil			9	16	0.13	80	0.010	2	1.14	0.002	0.06	0.1	0.09	1.9	0.2	0.05	7	1.2
L102W 87 50N	Soil			12	14	0.10	144	0.012	2	1.20	0.004	0.07	0.2	0.05	1.6	0.3	<0.05	9	0.6
L102W 88 00N	Soil			14	10	0.04	73	0.011	4	0.51	0.002	0.06	0.1	0.09	1.1	0.2	<0.05	4	0.8
L102W 89 00N	Soil			8	20	0.25	100	0.006	3	2.04	0.005	0.08	0.1	0.23	2.3	0.2	<0.05	5	0.7
L102W 89 50N	Soil			9	18	0.21	86	0.006	3	1.97	0.005	0.07	0.2	0.19	2.5	0.4	<0.05	6	0.5
L102W 90 00N	Soil			12	16	0.15	92	0.009	3	1.33	0.004	0.09	0.1	0.11	1.2	0.3	<0.05	7	<0.5
L102W 90 50N	Soil			10	18	0.20	233	0.008	3	1.68	0.005	0.10	0.1	0.14	2.0	0.5	<0.05	6	0.7
L102W 91 00N	Soil			10	12	0.06	140	0.016	3	0.62	0.004	0.08	0.1	0.06	1.1	0.2	0.06	5	<0.5
L102W 91 50N	Soil			12	14	0.13	48	0.005	3	0.91	0.003	0.08	<0.1	0.07	2.0	0.4	<0.05	4	1.3
L102W 92 00N	Soil			9	10	0.03	38	0.004	2	0.51	0.003	0.04	0.1	0.06	0.8	0.2	<0.05	3	1.0
L102W 92 50N	Soil			13	12	0.16	159	0.003	<1	1.36	0.005	0.04	0.1	0.10	2.4	0.3	<0.05	4	1.2
L102W 93 00N	Soil			8	9	0.08	219	0.027	3	0.36	0.003	0.04	0.1	0.06	1.4	0.1	0.06	4	0.9
L102W 93 50N	Soil			12	10	0.15	373	0.004	2	1.06	0.005	0.05	<0.1	0.17	1.6	0.4	0.08	3	1.3
L102W 94 00N	Soil			17	15	0.14	206	0.006	1	1.54	0.004	0.06	0.2	0.16	1.8	0.2	<0.05	6	2.2
L102W 94 50N	Soil			10	12	0.08	141	0.008	2	0.99	0.003	0.06	0.1	0.12	1.4	0.2	<0.05	5	<0.5
L102W 95 00N	Soil			28	13	0.20	309	0.004	<1	1.42	0.006	0.07	0.1	0.13	2.8	0.3	<0.05	4	1.5
L102W 95 50N	Soil			9	12	0.07	57	0.005	<1	1.12	0.003	0.04	0.1	0.09	2.2	0.4	<0.05	6	1.0
L102W 96 00N	Soil			8	14	0.14	62	0.006	<1	1.20	0.004	0.05	0.1	0.10	1.9	0.3	<0.05	5	1.0

This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
Report Date: September 02, 2008

Page: 3 of 5 **Part** 1

CERTIFICATE OF ANALYSIS

SMI08000740.1

Method	Analyte	Unit	MDL	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15		
				Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	P
				ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	%		
				0.1	0.1	0.1	1	0.1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	2	0.01	0.001
L102W	96 50N	Soil		2.3	97.9	73.1	153	1.0	18.5	13.5	1224	5.30	51.6	1.5	15.5	0.8	14	0.3	4.0	0.7	82	0.06	0.101
L102W	97 00N	Soil		2.3	118.7	62.6	106	3.0	14.9	6.6	297	4.78	44.2	4.6	12.3	0.4	16	0.4	2.6	0.7	71	0.07	0.152
L102W	97 50N	Soil		2.2	47.9	58.1	116	2.1	11.6	5.6	316	4.10	48.4	1.3	8.7	0.7	12	0.2	2.6	1.2	65	0.04	0.099
L102W	98 00N	Soil		1.4	32.4	35.2	91	1.2	11.4	5.5	640	4.45	38.2	0.9	3.8	0.2	12	0.3	2.2	0.5	73	0.06	0.120
L102W	98 50N	Soil		4.3	83.1	226.7	222	2.8	20.9	16.1	1301	6.30	78.6	2.0	96.7	1.1	20	0.4	7.3	5.3	57	0.14	0.096
L102W	99 00N	Soil		2.0	90.2	123.5	456	1.1	21.5	13.0	2522	4.49	81.3	4.9	5.7	1.1	22	2.7	2.1	1.9	58	0.25	0.165
L102W	99 50N	Soil		1.3	23.1	79.8	107	0.5	7.4	4.8	455	3.52	36.7	0.9	10.5	0.4	7	<0.1	1.7	2.1	57	0.02	0.066
L102W	100 00N	Soil		2.2	41.5	135.9	186	1.0	15.6	8.4	698	5.41	42.5	2.0	12.7	1.3	8	0.5	1.5	2.4	53	0.04	0.119
L102W	100 50N	Soil		2.9	48.3	132.4	147	0.2	8.9	5.3	351	4.00	42.6	2.1	22.6	1.7	9	0.1	2.1	1.8	56	0.05	0.118
L102W	101 00N	Soil		0.7	4.0	11.9	36	<0.1	2.0	4.0	385	2.58	30.9	1.0	12.7	4.0	3	<0.1	0.2	1.4	30	0.02	0.056
L102W	101 50N	Soil		0.9	3.2	4.9	31	0.1	1.3	1.6	534	2.10	10.8	1.4	2.4	4.2	2	<0.1	0.1	0.7	40	<0.01	0.046
L102W	102 00N	Soil		1.5	22.8	53.0	61	0.1	6.4	4.8	704	4.43	32.3	2.6	3.2	0.3	9	0.2	1.9	0.9	84	0.03	0.083
L102W	102 50N	Soil		3.2	30.1	74.3	78	0.4	8.2	4.2	348	5.50	54.3	0.8	7.4	0.6	8	0.2	2.9	0.8	71	0.03	0.104
L14W	76 00N	Soil		3.2	90.6	130.3	275	0.7	20.8	13.6	1627	4.36	85.2	1.5	32.5	1.9	35	1.0	3.9	1.8	48	0.34	0.096
L14W	76 50N	Soil		2.4	74.8	78.6	198	0.3	13.4	8.7	689	4.35	65.7	1.0	21.5	1.1	10	0.2	3.4	1.2	49	0.05	0.080
L14W	77 00N	Soil		2.5	71.8	88.8	194	0.3	13.0	8.9	704	4.62	71.4	1.0	21.7	1.4	11	0.3	3.5	1.5	53	0.06	0.065
L14W	77 50N	Soil		1.6	24.9	21.2	121	0.6	8.1	7.3	3039	3.40	28.7	1.1	9.6	0.7	13	0.6	1.2	0.6	54	0.05	0.069
L14W	78 00N	Soil		1.1	41.4	47.7	86	0.6	11.0	3.4	107	1.82	27.5	2.0	9.2	0.1	12	0.4	0.8	0.3	31	0.05	0.072
L14W	79 50N	Soil		2.5	73.6	85.1	227	0.6	20.2	15.2	975	4.43	61.4	1.5	23.4	1.8	30	0.7	3.3	1.1	49	0.27	0.116
L14W	80 00N	Soil		1.5	16.0	45.6	75	0.2	4.9	6.3	791	4.33	39.9	0.8	9.1	0.7	6	0.2	1.1	0.7	45	0.02	0.106
L14W	80 50N	Soil		2.9	101.4	129.8	321	0.5	27.0	15.2	430	4.70	102.9	1.9	41.6	3.4	13	0.7	3.4	2.4	50	0.12	0.109
L14W	81 00N	Soil		2.4	83.8	75.2	268	0.4	17.9	12.2	1239	4.87	61.0	1.7	18.6	1.7	17	0.9	2.5	1.0	50	0.23	0.135
L14W	81 50N	Soil		2.7	64.4	31.5	110	0.4	6.5	3.7	165	2.78	33.3	0.6	9.6	<0.1	13	0.2	2.0	0.5	59	0.06	0.072
L14W	82 00N	Soil		2.7	61.8	39.1	107	0.2	11.1	4.5	261	3.30	36.9	0.6	8.4	<0.1	18	0.2	1.9	0.8	71	0.10	0.067
L14W	82 50N	Soil		3.0	75.3	103.3	223	0.9	14.2	7.2	535	6.73	79.8	1.3	15.1	2.2	8	0.9	2.4	1.4	55	0.04	0.133
L14W	83 00N	Soil		2.1	45.3	41.3	103	0.4	12.1	3.5	160	4.28	32.1	0.8	11.2	0.1	20	0.1	1.3	0.6	61	0.06	0.075
L14W	83 50N	Soil		2.2	30.9	17.4	83	0.1	7.2	4.8	219	2.60	38.3	0.4	9.2	0.2	11	0.2	1.7	0.5	74	0.04	0.038
L14W	84 00N	Soil		3.1	74.8	90.8	142	1.3	12.3	10.9	1696	3.98	44.8	1.8	9.1	0.2	37	1.2	2.0	0.7	45	0.33	0.185
L14W	84 50N	Soil		3.1	68.9	82.1	120	0.5	11.7	4.6	360	4.11	46.4	1.1	16.6	<0.1	17	0.3	2.1	1.6	54	0.15	0.135
L14W	85 00N	Soil		3.6	53.0	46.8	134	0.2	12.1	6.1	245	3.93	56.9	0.7	8.6	<0.1	14	0.3	2.1	0.8	66	0.11	0.113

This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.

CERTIFICATE OF ANALYSIS

SMI08000740.1

Method	Analyte	Unit	MDL	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
				La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
				ppm	ppm	%	ppm	%	ppm	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
				1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.05	1	0.5	
L102W 96 50N	Soil			9	22	0.33	66	0.017	2	1.78	0.004	0.06	0.2	0.22	4.5	0.2	<0.05	6	1.1
L102W 97 00N	Soil			13	23	0.25	95	0.007	1	2.60	0.006	0.07	0.2	0.41	2.0	0.3	<0.05	7	0.9
L102W 97 50N	Soil			9	16	0.23	76	0.007	1	1.52	0.006	0.06	0.1	0.13	2.4	0.2	<0.05	6	1.0
L102W 98 00N	Soil			5	18	0.20	79	0.010	1	1.29	0.005	0.07	0.1	0.14	1.3	0.2	<0.05	7	<0.5
L102W 98 50N	Soil			11	22	0.31	98	0.009	2	2.32	0.006	0.06	0.1	0.26	3.6	0.2	<0.05	5	3.5
L102W 99 00N	Soil			20	16	0.14	372	0.005	<1	1.78	0.005	0.08	0.2	0.12	5.0	0.3	<0.05	7	0.6
L102W 99 50N	Soil			11	9	0.04	61	0.008	<1	0.79	0.003	0.06	0.2	0.04	1.0	0.4	<0.05	5	<0.5
L102W 100 00N	Soil			8	20	0.24	74	0.007	1	2.54	0.005	0.06	0.1	0.19	2.3	0.2	<0.05	7	0.8
L102W 100 50N	Soil			10	14	0.18	58	0.004	<1	1.90	0.004	0.05	0.2	0.14	1.8	0.3	<0.05	6	1.0
L102W 101 00N	Soil			22	2	0.02	35	0.001	1	0.81	0.002	0.06	<0.1	0.02	0.7	0.7	<0.05	4	<0.5
L102W 101 50N	Soil			30	2	0.04	41	0.001	<1	1.25	0.003	0.04	<0.1	0.03	1.3	1.3	<0.05	6	<0.5
L102W 102 00N	Soil			9	14	0.15	47	0.012	<1	1.55	0.005	0.05	0.2	0.09	1.3	0.3	<0.05	9	0.7
L102W 102 50N	Soil			5	19	0.17	48	0.010	1	2.10	0.005	0.04	0.2	0.18	1.9	0.3	<0.05	8	0.7
L14W 76 00N	Soil			14	14	0.29	201	0.007	2	1.28	0.009	0.09	0.1	0.18	4.6	0.2	0.05	4	0.7
L14W 76 50N	Soil			9	14	0.21	62	0.005	<1	1.21	0.005	0.05	0.1	0.11	2.6	0.2	<0.05	4	1.2
L14W 77 00N	Soil			9	14	0.21	67	0.008	2	1.26	0.005	0.06	0.1	0.14	2.9	0.2	<0.05	5	0.8
L14W 77 50N	Soil			9	13	0.08	167	0.005	1	1.40	0.005	0.05	0.1	0.12	2.9	0.2	<0.05	5	0.9
L14W 78 00N	Soil			17	15	0.19	109	0.009	<1	1.53	0.008	0.05	<0.1	0.21	1.9	0.2	0.10	6	1.5
L14W 79 50N	Soil			13	14	0.27	144	0.008	1	1.31	0.010	0.06	0.2	0.23	4.9	0.2	<0.05	3	0.7
L14W 80 00N	Soil			8	10	0.13	50	0.004	1	1.17	0.004	0.05	0.1	0.11	1.6	0.2	<0.05	5	<0.5
L14W 80 50N	Soil			15	15	0.25	99	0.005	2	2.18	0.005	0.06	0.1	0.22	5.3	0.2	<0.05	4	2.0
L14W 81 00N	Soil			15	15	0.31	89	0.006	<1	1.47	0.005	0.05	<0.1	0.18	6.5	0.1	<0.05	4	0.6
L14W 81 50N	Soil			11	9	0.03	62	0.009	7	0.43	0.005	0.05	0.1	0.03	1.3	<0.1	<0.05	4	1.2
L14W 82 00N	Soil			8	10	0.07	89	0.009	3	0.62	0.004	0.05	0.1	0.10	1.1	<0.1	0.07	6	<0.5
L14W 82 50N	Soil			8	17	0.21	94	0.007	1	3.05	0.005	0.04	0.2	0.28	3.3	0.2	<0.05	8	1.2
L14W 83 00N	Soil			5	12	0.08	65	0.008	4	1.04	0.005	0.03	0.1	0.17	1.7	0.1	0.08	5	0.9
L14W 83 50N	Soil			9	7	0.03	66	0.006	3	0.38	0.003	0.04	0.1	0.05	1.0	0.2	<0.05	5	0.6
L14W 84 00N	Soil			18	11	0.14	128	0.004	2	1.60	0.007	0.05	0.1	0.18	1.4	0.2	0.07	5	1.2
L14W 84 50N	Soil			8	10	0.07	99	0.004	3	0.84	0.005	0.05	<0.1	0.13	0.7	0.1	<0.05	5	0.9
L14W 85 00N	Soil			6	10	0.09	59	0.004	2	0.71	0.004	0.04	<0.1	0.08	1.1	0.1	<0.05	7	0.7



AcmeLabs
 ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
Report Date: September 02, 2008

Page: 4 of 5 **Part** 1

CERTIFICATE OF ANALYSIS

SMI08000740.1

	Method	Analyte	Unit	MDL	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15			
					Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	P	
					ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	%
					0.1	0.1	0.1	1	0.1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	0.001
L14W	85 50N	Soil			3.1	61.5	91.0	164	0.3	12.0	9.7	1281	6.31	47.8	0.7	33.9	0.3	8	0.5	2.0	3.0	73	0.02	0.080	
L14W	86 00N	Soil			2.4	45.9	33.3	119	0.3	9.9	5.0	208	4.08	47.2	0.6	7.4	0.1	7	0.2	1.7	0.8	81	0.03	0.050	
L14W	86 50N	Soil			2.4	64.2	68.6	134	0.5	13.1	8.1	733	5.11	50.8	0.8	13.7	0.2	14	0.3	2.2	0.7	71	0.15	0.085	
L14W	87 00N	Soil			1.4	33.9	56.0	74	0.3	12.8	7.9	1230	5.64	29.2	1.0	3.3	0.3	12	0.5	1.4	0.4	62	0.07	0.072	
L14W	87 50N	Soil			2.9	67.6	102.6	119	0.3	11.9	8.2	1855	4.80	95.2	0.7	11.4	0.1	16	0.3	2.5	0.9	77	0.04	0.111	
L14W	88 00N	Soil			3.3	59.3	75.4	117	0.7	12.3	6.0	406	5.67	47.3	0.9	8.5	0.3	8	0.3	2.0	0.7	57	0.04	0.107	
L14W	88 50N	Soil			3.1	62.3	87.2	128	0.3	9.5	7.9	748	5.32	59.1	1.2	14.7	0.5	9	0.2	3.1	1.0	90	0.06	0.110	
L14W	89 00N	Soil			2.6	47.3	42.5	98	0.5	11.3	5.4	372	3.52	40.2	1.5	21.5	<0.1	29	0.4	2.9	0.3	74	0.29	0.089	
L14W	89 50N	Soil			1.6	29.6	28.7	90	0.1	8.7	11.4	395	4.41	63.6	0.8	2.4	1.1	26	0.2	1.9	0.4	96	0.29	0.036	
L14W	90 00N	Soil			1.8	39.6	42.0	89	0.1	8.6	5.2	446	4.30	43.7	0.8	3.8	0.2	14	<0.1	3.1	0.6	83	0.07	0.141	
L14W	90 50N	Soil			1.3	52.1	44.7	81	0.6	8.0	4.2	370	3.12	25.7	0.9	3.6	<0.1	15	0.7	2.0	0.5	61	0.12	0.098	
L14W	91 00N	Soil			1.4	36.3	77.8	82	0.4	8.8	6.8	1570	4.02	31.9	0.9	3.0	0.1	9	0.5	1.9	0.6	64	0.04	0.079	
L14W	91 50N	Soil			2.5	41.7	68.3	158	0.5	11.6	8.0	875	4.78	57.6	1.1	25.4	0.1	16	0.2	3.7	1.2	78	0.11	0.114	
L14W	92 00N	Soil			1.6	33.9	55.3	161	0.2	8.2	5.1	363	4.30	139.1	0.6	7.6	0.2	13	0.2	5.6	1.5	67	0.10	0.057	
L14W	92 50N	Soil			1.6	44.9	63.3	138	0.4	8.0	9.0	2495	3.91	59.4	0.9	7.6	0.1	17	0.6	3.6	1.8	63	0.14	0.080	
L14W	93 00N	Soil			2.4	30.2	17.4	69	<0.1	5.7	4.6	397	2.55	42.8	0.4	20.9	0.1	8	0.2	2.9	1.1	77	0.02	0.031	
L14W	93 50N	Soil			1.3	18.2	30.3	78	<0.1	8.5	3.5	260	3.44	42.4	0.5	4.0	<0.1	11	0.2	2.1	0.9	62	0.07	0.079	
L14W	94 00N	Soil			5.6	29.7	25.5	44	0.3	5.4	3.6	219	4.03	19.1	0.7	8.9	0.7	5	0.3	1.4	0.9	41	0.03	0.075	
L14W	94 50N	Soil			2.9	31.4	60.8	104	0.8	7.9	5.8	349	5.30	50.8	0.7	5.1	0.1	17	0.5	2.5	1.9	68	0.21	0.078	
L14W	95 00N	Soil			1.9	26.6	33.0	54	0.5	5.5	4.1	858	6.16	31.8	0.3	21.6	0.2	5	0.9	1.9	1.3	63	0.03	0.174	
L14W	95 50N	Soil			4.0	45.5	38.5	58	0.7	5.2	10.7	3376	8.87	26.1	0.5	10.9	1.0	5	0.4	1.9	1.1	71	0.02	0.402	
L14W	96 00N	Soil			11.0	51.9	37.5	78	0.9	7.4	4.5	467	4.25	55.5	0.8	3.2	<0.1	13	0.5	2.0	0.8	79	0.02	0.067	
L14W	96 50N	Soil			4.2	131.2	52.4	124	0.9	10.6	5.4	413	4.60	45.0	1.1	6.2	0.2	20	0.5	1.6	0.9	74	0.11	0.098	
L14W	97 00N	Soil			1.7	51.9	39.3	78	0.5	5.9	3.7	288	3.60	32.4	0.6	8.1	0.2	10	0.1	1.3	0.8	77	0.02	0.096	
L14W	97 50N	Soil			3.8	111.3	56.1	119	0.2	8.2	5.4	379	4.90	59.5	0.8	8.5	1.2	11	<0.1	2.4	1.5	74	0.02	0.150	
L14W	98 00N	Soil			8.2	90.1	88.4	112	0.3	12.6	9.0	504	5.40	83.8	0.8	10.9	1.0	8	0.2	2.0	1.0	60	0.02	0.090	
L14W	98 50N	Soil			30.7	147.5	22.0	41	2.0	4.4	12.6	1052	4.50	43.1	1.0	29.1	0.8	11	0.2	0.9	0.7	78	0.09	0.228	
L14W	99 00N	Soil			2.8	44.2	30.9	116	0.9	10.7	4.3	220	3.40	23.4	1.9	1.9	0.1	21	0.2	1.8	0.4	60	0.06	0.048	
L14W	99 50N	Soil			I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	
L14W	100 00N	Soil			21.1	113.1	35.4	73	0.6	9.9	6.6	300	4.50	23.2	1.9	7.7	0.1	12	0.5	1.3	0.5	80	0.02	0.086	

This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
 Report Date: September 02, 2008

Page: 4 of 5 Part 2

CERTIFICATE OF ANALYSIS

SMI08000740.1

Method	Analyte	Unit	MDL	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15		
				La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
				ppm	ppm	%	ppm	%	ppm	%	ppm	ppm	ppm	ppm	%	ppm	ppm		
				1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.05	1	0.5		
L14W	85 50N	Soil		8	14	0.12	111	0.007	1	1.49	0.004	0.04	0.1	0.10	1.6	0.1	<0.05	9	1.1
L14W	86 00N	Soil		7	11	0.05	46	0.006	2	0.67	0.004	0.03	<0.1	0.11	1.5	0.2	<0.05	7	1.1
L14W	86 50N	Soil		7	14	0.11	103	0.006	2	1.04	0.004	0.05	0.1	0.11	1.2	0.2	<0.05	6	0.9
L14W	87 00N	Soil		5	15	0.20	86	0.009	2	1.36	0.005	0.04	0.1	0.12	1.2	0.2	<0.05	9	1.2
L14W	87 50N	Soil		7	14	0.09	309	0.009	2	0.86	0.004	0.04	<0.1	0.06	1.2	0.3	<0.05	7	0.7
L14W	88 00N	Soil		6	16	0.18	50	0.007	1	1.64	0.004	0.03	0.1	0.19	1.8	0.2	0.06	5	0.9
L14W	88 50N	Soil		10	15	0.14	43	0.013	2	1.12	0.004	0.04	0.1	0.10	2.3	0.2	<0.05	9	0.8
L14W	89 00N	Soil		7	15	0.11	69	0.008	3	1.31	0.007	0.07	0.2	0.07	1.4	0.2	<0.05	6	0.8
L14W	89 50N	Soil		8	15	0.15	97	0.005	1	1.11	0.007	0.05	0.2	0.03	3.3	0.1	<0.05	7	<0.5
L14W	90 00N	Soil		8	16	0.14	53	0.012	3	0.93	0.005	0.06	0.1	0.04	1.6	0.1	<0.05	7	<0.5
L14W	90 50N	Soil		14	11	0.06	66	0.007	<1	0.83	0.004	0.05	0.1	0.08	1.1	<0.1	<0.05	4	0.5
L14W	91 00N	Soil		11	18	0.09	53	0.013	2	1.31	0.004	0.05	0.1	0.09	1.4	0.1	<0.05	8	<0.5
L14W	91 50N	Soil		8	15	0.17	59	0.012	1	1.12	0.004	0.07	<0.1	0.07	1.4	0.2	<0.05	7	0.5
L14W	92 00N	Soil		6	12	0.11	90	0.008	1	0.95	0.004	0.07	0.1	0.06	2.0	0.2	<0.05	6	0.9
L14W	92 50N	Soil		10	12	0.08	92	0.006	1	1.08	0.004	0.07	0.1	0.08	1.2	0.3	<0.05	5	<0.5
L14W	93 00N	Soil		9	11	0.04	66	0.009	2	0.58	0.003	0.05	0.1	0.02	1.0	0.2	<0.05	5	<0.5
L14W	93 50N	Soil		6	17	0.14	50	0.008	3	1.28	0.003	0.07	0.1	0.07	1.2	0.2	<0.05	7	0.6
L14W	94 00N	Soil		6	11	0.06	33	0.008	1	2.64	0.004	0.05	0.3	0.12	2.4	0.2	<0.05	6	0.6
L14W	94 50N	Soil		9	10	0.08	68	0.009	<1	1.01	0.005	0.05	0.2	0.07	1.4	0.2	<0.05	8	0.9
L14W	95 00N	Soil		10	9	0.12	53	0.005	2	1.53	0.005	0.05	0.2	0.08	1.4	0.2	<0.05	8	1.3
L14W	95 50N	Soil		4	16	0.17	54	0.007	<1	2.52	0.004	0.04	0.1	0.18	2.1	0.2	0.06	8	1.6
L14W	96 00N	Soil		5	17	0.13	76	0.012	1	1.42	0.004	0.07	0.2	0.11	1.1	0.2	<0.05	9	0.8
L14W	96 50N	Soil		8	19	0.28	96	0.011	2	1.95	0.005	0.06	0.1	0.27	1.4	0.2	<0.05	9	0.8
L14W	97 00N	Soil		7	12	0.11	48	0.008	<1	1.20	0.004	0.06	<0.1	0.05	1.2	0.3	<0.05	8	<0.5
L14W	97 50N	Soil		8	15	0.19	62	0.006	<1	1.67	0.004	0.06	0.1	0.06	2.4	0.3	<0.05	8	0.6
L14W	98 00N	Soil		5	18	0.26	64	0.005	<1	2.40	0.004	0.06	0.1	0.13	2.5	0.2	<0.05	7	1.0
L14W	98 50N	Soil		6	10	0.33	42	0.019	<1	4.88	0.010	0.04	<0.1	0.22	2.5	0.3	0.08	8	2.2
L14W	99 00N	Soil		42	17	0.18	88	0.010	2	1.66	0.006	0.05	0.1	0.11	1.7	0.3	<0.05	7	0.5
L14W	99 50N	Soil		I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.
L14W	100 00N	Soil		11	17	0.24	72	0.010	<1	1.83	0.004	0.05	0.2	0.11	1.4	0.2	<0.05	10	0.5



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**

110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo

Report Date: September 02, 2008

Page: 5 of 5 Part 1

CERTIFICATE OF ANALYSIS

SMI08000740.1

Method	Analyte	Unit	MDL	1DX15 Mo	1DX15 Cu	1DX15 Pb	1DX15 Zn	1DX15 Ag	1DX15 Ni	1DX15 Co	1DX15 Mn	1DX15 Fe	1DX15 As	1DX15 U	1DX15 Au	1DX15 Th	1DX15 Sr	1DX15 Cd	1DX15 Sb	1DX15 Bi	1DX15 V	1DX15 Ca	1DX15 P
				ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	%
				0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	0.001
L14W	100 50N	Soil		8.4	37.2	25.4	39	0.3	4.0	3.1	275	3.21	19.1	0.5	11.9	0.1	8	<0.1	0.9	0.9	72	0.01	0.066
L14W	101 00N	Soil		25.4	74.0	22.8	45	0.8	8.8	4.7	176	2.79	18.7	1.7	25.0	0.1	19	0.1	0.9	0.8	54	0.08	0.074
L14W	101 50N	Soil		17.7	35.2	35.7	53	0.4	8.6	4.0	269	5.45	20.4	0.8	5.0	0.5	9	0.2	1.4	0.5	91	0.07	0.077
L14W	102 00N	Soil		3.3	18.4	14.6	40	0.2	6.8	4.0	251	3.47	16.8	0.5	6.1	<0.1	8	0.1	1.1	0.4	91	0.01	0.046
L14W	102 50N	Soil		24.0	233.3	17.2	4	2.6	1.2	9.1	340	0.37	2.1	53.8	6.4	0.3	1	<0.1	0.1	<0.1	12	0.02	0.312
L14W	103 00N	Soil		I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.
L14W	103 50N	Soil		36.9	41.1	40.1	31	0.5	3.9	3.2	198	6.32	35.8	1.0	35.2	0.2	6	0.2	1.1	1.3	123	0.02	0.146
L14W	104 00N	Soil		57.4	1312	17.8	16	2.9	6.6	27.4	714	5.46	921.0	9.3	48.1	1.5	12	0.5	5.7	0.6	8	0.08	0.074
L14W	104 50N	Soil		51.8	1340	58.6	164	0.4	13.2	18.2	774	5.20	68.6	1.9	38.9	0.7	77	0.3	3.8	0.8	68	0.27	0.085
L14W	105 00N	Soil		76.1	125.1	18.5	26	1.5	3.3	2.6	163	7.26	10.6	0.8	16.6	1.2	4	0.1	0.6	0.7	81	0.03	0.106
L14W	105 50N	Soil		I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.
L14W	106 00N	Soil		6.3	328.5	59.4	100	0.5	19.1	8.3	333	5.53	31.0	0.8	27.6	2.3	6	0.2	1.9	0.6	55	0.05	0.070
L14W	106 50N	Soil		5.8	158.6	47.8	94	0.4	10.5	6.8	458	5.01	41.1	1.2	36.5	1.2	7	0.2	1.8	1.0	62	0.03	0.089
L14W	107 00N	Soil		4.1	157.1	31.7	50	0.5	7.9	4.3	184	2.95	31.2	1.4	34.1	0.2	14	0.2	0.9	0.9	51	0.06	0.082
L14W	107 50N	Soil		4.0	120.8	22.3	36	1.7	3.3	2.1	116	1.94	16.7	1.0	34.8	0.1	19	0.2	0.5	1.0	38	0.08	0.055
L14W	108 00N	Soil		6.5	325.3	35.2	83	0.6	15.9	13.7	1296	3.74	36.3	1.4	33.0	0.8	34	0.3	1.6	0.7	50	0.15	0.101
L14W	108 50N	Soil		7.1	329.7	30.2	77	0.8	11.3	7.6	271	6.27	69.2	1.7	53.2	1.3	18	0.3	2.9	0.7	56	0.11	0.094
L14W	109 00N	Soil		7.4	206.0	32.7	87	0.8	11.2	8.2	472	4.27	83.2	1.4	24.5	0.3	30	0.2	2.1	3.2	62	0.11	0.090
L14W	109 50N	Soil		27.2	1035	23.0	62	0.2	18.0	22.5	1593	4.02	32.4	0.7	27.6	1.1	91	0.2	1.1	0.4	53	0.42	0.075
L14W	110 00N	Soil		8.5	388.4	34.1	74	0.5	11.5	6.8	403	5.98	42.3	1.0	35.8	1.5	27	0.1	1.6	0.8	82	0.10	0.058
L14W	110 50N	Soil		2.6	90.2	37.5	107	0.1	14.4	8.1	357	4.38	31.0	1.1	13.0	1.5	12	0.2	1.3	0.5	60	0.06	0.066
L14W	111 00N	Soil		0.8	22.9	15.1	41	0.4	12.2	17.1	809	1.76	5.9	1.1	4.7	0.3	10	<0.1	0.4	0.2	47	0.03	0.051
L14W	111 50N	Soil		1.8	34.0	31.0	63	0.4	11.5	4.2	216	5.85	33.9	0.7	8.8	1.5	7	0.1	1.2	0.7	102	0.02	0.058
L14W	112 00N	Soil		1.3	15.0	15.7	31	0.2	7.1	2.6	104	1.77	14.3	0.4	5.7	<0.1	10	0.1	0.5	0.3	63	0.04	0.048
L14W	112 50N	Soil		1.2	23.1	14.9	70	0.2	21.2	19.2	3168	3.52	11.4	0.8	17.2	0.3	18	0.3	0.4	0.2	60	0.12	0.103



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
Report Date: September 02, 2008

Page: 5 of 5 **Part** 2

CERTIFICATE OF ANALYSIS

SMI08000740.1

Method	Analyte	Unit	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
			La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
		MDL	ppm	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	
			1	1	0.01	1	0.001	0.01	0.001	0.01	0.1	0.01	0.1	0.05	1	0.5	0.5	
L14W	100 50N	Soil	7	9	0.12	61	0.006	<1	1.31	0.004	0.06	0.1	0.04	1.0	0.6	<0.05	9	0.7
L14W	101 00N	Soil	14	13	0.27	118	0.005	<1	1.62	0.006	0.08	0.1	0.04	0.9	0.3	<0.05	7	1.6
L14W	101 50N	Soil	5	16	0.58	43	0.023	1	2.00	0.007	0.14	0.1	0.06	2.9	0.4	<0.05	12	1.3
L14W	102 00N	Soil	5	13	0.17	40	0.019	2	1.35	0.005	0.05	0.1	0.06	1.3	0.2	0.14	9	<0.5
L14W	102 50N	Soil	9	5	0.01	6	0.015	<1	7.76	0.005	0.01	<0.1	0.16	2.9	<0.1	0.09	<1	3.6
L14W	103 00N	Soil	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.
L14W	103 50N	Soil	6	9	0.13	31	0.006	1	1.41	0.004	0.04	0.2	0.09	0.5	0.2	0.06	10	1.8
L14W	104 00N	Soil	20	1	0.02	119	<0.001	4	>10	0.002	<0.01	<0.1	0.65	9.3	<0.1	0.61	<1	5.1
L14W	104 50N	Soil	40	13	0.23	80	0.006	2	1.57	0.007	0.06	0.2	0.29	4.1	0.2	<0.05	6	4.9
L14W	105 00N	Soil	5	7	0.22	33	0.015	2	1.81	0.006	0.04	0.2	0.13	1.3	0.4	<0.05	12	1.6
L14W	105 50N	Soil	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.
L14W	106 00N	Soil	5	24	0.30	55	0.002	1	2.83	0.005	0.05	<0.1	0.17	3.6	0.3	<0.05	5	1.6
L14W	106 50N	Soil	6	16	0.19	40	0.004	<1	2.16	0.003	0.04	0.1	0.15	1.9	0.2	<0.05	6	1.4
L14W	107 00N	Soil	8	12	0.30	66	0.006	1	1.88	0.005	0.08	0.1	0.16	1.1	0.3	<0.05	7	0.9
L14W	107 50N	Soil	11	8	0.12	86	0.003	1	1.42	0.006	0.06	<0.1	0.14	0.4	0.3	<0.05	6	<0.5
L14W	108 00N	Soil	11	13	0.26	104	0.003	1	1.86	0.005	0.07	<0.1	0.13	2.1	0.2	<0.05	4	0.8
L14W	108 50N	Soil	13	13	0.28	56	0.006	<1	2.08	0.004	0.05	<0.1	0.35	3.1	0.2	<0.05	5	3.4
L14W	109 00N	Soil	9	13	0.21	84	0.006	1	1.53	0.004	0.06	0.1	0.11	1.4	0.2	<0.05	5	0.9
L14W	109 50N	Soil	15	17	0.30	250	0.002	1	1.73	0.007	0.08	<0.1	0.07	2.8	0.2	<0.05	5	2.8
L14W	110 00N	Soil	8	19	0.25	71	0.006	2	2.59	0.005	0.04	0.1	0.13	2.9	0.2	<0.05	8	2.3
L14W	110 50N	Soil	7	18	0.28	58	0.008	3	2.84	0.005	0.03	0.1	0.18	3.3	0.2	<0.05	5	1.1
L14W	111 00N	Soil	10	16	0.23	78	0.004	1	2.01	0.005	0.05	<0.1	0.08	2.4	0.3	<0.05	6	<0.5
L14W	111 50N	Soil	5	23	0.19	42	0.019	<1	2.93	0.004	0.04	<0.1	0.14	3.5	0.2	<0.05	8	1.2
L14W	112 00N	Soil	4	12	0.12	60	0.008	1	1.04	0.004	0.04	<0.1	0.11	0.9	0.1	<0.05	7	<0.5
L14W	112 50N	Soil	5	23	0.30	115	0.006	2	2.19	0.006	0.07	<0.1	0.07	2.0	0.2	<0.05	6	0.7

QUALITY CONTROL REPORT

SMI08000740.1

Method	Analyte	Unit	MDL	1DX15 Mo	1DX15 Cu	1DX15 Pb	1DX15 Zn	1DX15 Ag	1DX15 Ni	1DX15 Co	1DX15 Mn	1DX15 Fe	1DX15 As	1DX15 U	1DX15 Au	1DX15 Th	1DX15 Sr	1DX15 Cd	1DX15 Sb	1DX15 Bi	1DX15 V	1DX15 Ca	1DX15 P
				ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	%
Pulp Duplicates																							
L102W 88 00N	Soil			2.2	59.5	99.6	214	1.0	8.9	4.7	502	3.64	69.9	0.8	22.4	0.3	14	0.4	2.2	2.5	71	0.06	0.091
REP L102W 88 00N	QC			2.0	58.9	98.4	217	1.0	9.3	4.9	508	3.67	70.4	0.9	22.5	0.3	13	0.3	2.1	2.4	71	0.06	0.085
L102W 96 50N	Soil			2.3	97.9	73.1	153	1.0	18.5	13.5	1224	5.30	51.6	1.5	15.5	0.8	14	0.3	4.0	0.7	82	0.06	0.101
REP L102W 96 50N	QC			2.5	100.7	75.0	163	1.0	17.9	14.0	1255	5.41	52.0	1.6	13.3	1.0	14	0.5	4.1	0.7	84	0.05	0.099
L14W 99 00N	Soil			2.8	44.2	30.9	116	0.9	10.7	4.3	220	3.40	23.4	1.9	1.9	0.1	21	0.2	1.8	0.4	60	0.06	0.048
REP L14W 99 00N	QC			3.1	46.4	33.4	124	0.9	10.9	4.9	234	3.70	24.4	2.0	4.7	0.1	22	0.3	2.1	0.4	64	0.06	0.050
Reference Materials																							
STD DS7	Standard			20.0	118.9	76.4	405	0.8	54.7	9.8	690	2.48	51.3	5.5	75.3	4.5	78	6.4	6.8	5.0	88	0.95	0.075
STD DS7	Standard			19.7	116.5	76.9	407	0.8	55.1	9.6	680	2.45	51.5	5.7	74.7	4.9	79	6.0	6.6	5.0	86	0.94	0.070
STD DS7	Standard			20.1	113.2	80.5	419	0.9	59.6	9.9	650	2.48	53.6	5.6	66.2	4.7	77	6.3	6.9	5.2	89	0.95	0.076
STD DS7	Standard			19.6	109.7	75.5	391	0.8	55.1	8.8	620	2.32	50.1	5.3	67.5	4.5	72	5.7	6.4	4.7	84	0.88	0.073
STD DS7	Standard			18.5	113.5	74.9	403	0.8	54.6	9.9	670	2.51	49.1	5.3	82.4	4.5	68	6.0	6.1	4.8	86	0.90	0.074
STD DS7	Standard			21.7	121.7	78.4	409	0.9	58.6	9.8	673	2.54	50.2	5.7	68.9	4.8	78	6.3	6.3	4.8	88	0.95	0.073
STD DS7	Standard			16.7	110.0	66.8	376	0.8	55.3	8.8	608	2.33	49.9	4.8	66.4	4.7	72	5.4	5.3	4.3	89	0.91	0.070
STD DS7	Standard			19.4	104.7	69.6	370	0.8	55.1	9.6	602	2.38	49.7	5.1	126.4	4.5	73	5.3	5.4	4.4	91	0.93	0.071
STD DS7 Expected				20.9	109	70.6	411	0.9	56	9.7	627	2.39	48.2	4.9	70	4.4	69	6.4	5.9	4.5	86	0.93	0.08
BLK	Blank			<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01	<0.001
BLK	Blank			<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01	<0.001
BLK	Blank			<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01	<0.001
BLK	Blank			<0.1	0.5	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01	<0.001

QUALITY CONTROL REPORT

SMI08000740.1

Method	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se	
Unit	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
MDL	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5	
Pulp Duplicates																	
L102W 88 00N	Soil	14	10	0.04	73	0.011	4	0.51	0.002	0.06	0.1	0.09	1.1	0.2	<0.05	4	0.8
REP L102W 88 00N	QC	13	10	0.04	72	0.008	3	0.47	0.002	0.06	0.1	0.15	1.0	0.2	<0.05	4	0.6
L102W 96 50N	Soil	9	22	0.33	66	0.017	2	1.78	0.004	0.06	0.2	0.22	4.5	0.2	<0.05	6	1.1
REP L102W 96 50N	QC	10	21	0.34	69	0.015	2	1.80	0.005	0.06	0.1	0.19	4.8	0.2	<0.05	6	0.9
L14W 99 00N	Soil	42	17	0.18	88	0.010	2	1.66	0.006	0.05	0.1	0.11	1.7	0.3	<0.05	7	0.5
REP L14W 99 00N	QC	45	17	0.19	94	0.010	<1	1.69	0.006	0.05	0.2	0.10	1.8	0.3	<0.05	8	1.1
Reference Materials																	
STD DS7	Standard	13	167	1.11	401	0.136	41	1.08	0.086	0.52	3.9	0.20	2.7	4.3	0.17	5	4.1
STD DS7	Standard	13	167	1.10	404	0.131	37	1.07	0.086	0.52	3.9	0.20	2.7	4.5	0.17	5	3.4
STD DS7	Standard	13	170	1.08	394	0.123	39	0.99	0.082	0.46	4.4	0.22	2.5	4.5	0.20	5	3.3
STD DS7	Standard	12	160	1.02	367	0.114	38	0.95	0.077	0.44	4.2	0.17	2.4	4.1	0.19	4	3.5
STD DS7	Standard	12	161	1.07	382	0.125	40	1.04	0.076	0.50	3.9	0.20	2.3	4.1	0.19	5	3.8
STD DS7	Standard	13	168	1.10	420	0.139	39	1.10	0.087	0.51	4.0	0.21	2.6	4.4	0.19	5	3.4
STD DS7	Standard	12	163	0.98	345	0.118	36	0.95	0.069	0.42	3.5	0.17	2.3	4.2	0.18	5	2.9
STD DS7	Standard	12	166	1.05	346	0.119	37	0.98	0.074	0.45	3.9	0.20	2.3	4.1	0.18	5	3.2
STD DS7 Expected		13	163	1.05	370	0.124	39	0.959	0.073	0.44	3.8	0.2	2.5	4.2	0.21	4.6	3.5
BLK	Blank	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
BLK	Blank	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
BLK	Blank	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
BLK	Blank	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.

Vancouver BC V6C 1Z7 Canada

Submitted By:

Glen Garratt

Receiving Lab:

Canada-Smithers

Received:

August 13, 2008

Report Date:

September 03, 2008

Page:

1 of 2

CERTIFICATE OF ANALYSIS

SMI08000743.1

CLIENT JOB INFORMATION

Project: Zymo
Shipment ID: zy-rk-08-11
P.O. Number
Number of Samples: 14

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
DISP-RJT Dispose of Reject After 90 days

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Mincord Exploration Consultants Ltd.
110 - 325 Howe St.
Vancouver BC V6C 1Z7
Canada

CC: Bob Johnston

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status
R150	14	Crush, split and pulverize rock to 200 mesh		
1DX15	14	1:1:1 Aqua Regia digestion ICP-MS analysis	15	Completed

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only. All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.

Vancouver BC V6C 1Z7 Canada

Project:

Zymo

Report Date:

September 03, 2008

Page:

2 of 2

Part 1

CERTIFICATE OF ANALYSIS

SMI08000743.1

Method	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
Unit	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	
MDL	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	
726695	Rock	3.15	26.8	2907	7.2	64	0.9	4.4	11.7	447	6.00	19.6	1.9	343.2	11.9	82	0.2	1.2	0.2	92	0.30
726696	Rock	3.22	28.6	2797	8.7	66	0.8	3.9	11.9	553	5.56	144.1	2.4	330.8	12.9	109	0.2	15.6	0.2	63	0.41
726697	Rock	2.55	31.2	1128	8.8	42	0.9	1.9	11.6	711	5.55	172.3	2.8	190.1	13.8	23	0.1	19.4	0.1	57	0.21
726698	Rock	2.63	24.5	452.1	17.0	50	0.3	3.1	12.3	260	4.28	2.0	0.8	32.2	3.6	26	0.1	0.2	0.4	71	0.53
726699	Rock	1.79	7.5	288.1	9.7	35	0.1	2.9	9.2	153	3.36	2.0	1.0	33.3	4.4	16	<0.1	0.1	0.2	57	0.51
726700	Rock	2.66	6.5	2317	33.6	291	10.9	3.4	7.5	624	3.69	9.8	7.4	39.4	16.5	24	1.7	0.3	6.3	69	0.68
726701	Rock	1.81	7.1	203.0	12.2	59	0.5	3.6	7.2	674	4.36	6.2	5.8	7.2	15.2	67	0.2	0.2	1.7	84	2.03
726702	Rock	2.02	3.1	52.6	10.3	174	0.3	10.3	2.1	1159	2.75	4.6	2.3	17.6	13.7	50	0.6	<0.1	0.9	84	1.45
726703	Rock	2.25	2.2	73.2	9.9	17	<0.1	1.0	2.8	96	4.18	10.1	0.9	11.6	4.5	23	<0.1	1.7	0.5	58	0.30
726704	Rock	2.70	4.9	183.9	7.6	43	<0.1	5.7	10.1	373	2.88	2.1	2.1	10.7	8.8	60	0.1	<0.1	<0.1	86	0.66
726705	Rock	2.23	26.7	187.1	3.6	19	<0.1	4.0	5.0	197	1.63	0.5	0.1	7.2	0.7	109	<0.1	0.2	0.1	46	0.88
726706	Rock	2.34	27.6	192.6	9.0	13	0.2	9.1	8.3	94	3.13	2.5	0.2	28.3	1.6	6	<0.1	<0.1	0.2	27	0.26
726707	Rock	2.88	29.7	1035	10.4	36	0.4	4.9	21.4	229	4.72	3.5	0.9	78.1	5.7	9	<0.1	0.2	0.3	57	0.42
726708	Rock	3.26	80.8	508.0	14.3	25	0.3	3.3	15.4	348	2.31	13.0	3.6	50.0	12.8	24	0.2	3.0	0.1	28	0.27



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.

Vancouver BC V6C 1Z7 Canada

Project:

Zymo

Report Date:

September 03, 2008

Page:

2 of 2

Part 2

CERTIFICATE OF ANALYSIS

SMI08000743.1

Method	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se	
Unit	%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
MDL	0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5	
726695	Rock	0.103	12	13	0.21	407	0.012	2	0.47	0.034	0.22	<0.1	1.38	3.9	0.1	0.26	5	2.3
726696	Rock	0.133	16	5	0.11	397	0.003	2	0.34	0.024	0.24	<0.1	2.39	4.2	0.2	0.26	2	2.6
726697	Rock	0.110	10	4	0.02	112	0.001	1	0.37	0.015	0.24	<0.1	1.96	3.5	0.3	<0.05	2	1.6
726698	Rock	0.155	7	6	1.04	47	0.063	<1	1.73	0.064	0.19	0.1	0.08	3.3	0.3	0.96	6	3.5
726699	Rock	0.203	13	3	1.08	39	0.001	<1	1.65	0.058	0.13	<0.1	0.04	3.0	0.3	1.07	5	2.1
726700	Rock	0.135	20	6	1.13	125	0.002	1	1.87	0.034	0.10	4.0	0.45	4.1	0.1	0.58	8	0.7
726701	Rock	0.137	20	7	1.10	53	0.002	2	2.06	0.029	0.14	0.1	0.03	5.7	0.2	1.10	7	<0.5
726702	Rock	0.153	27	10	1.21	88	0.002	3	1.88	0.037	0.07	<0.1	0.05	6.2	<0.1	0.09	8	0.6
726703	Rock	0.203	7	2	0.58	114	0.002	<1	1.22	0.044	0.13	<0.1	0.06	2.8	0.2	0.28	6	2.1
726704	Rock	0.138	18	7	1.15	143	0.109	2	1.53	0.065	0.12	<0.1	0.02	4.1	0.1	0.16	6	0.5
726705	Rock	0.014	4	8	0.58	258	0.004	1	1.07	0.043	0.25	<0.1	0.03	3.5	0.3	0.48	3	0.5
726706	Rock	0.143	4	13	0.36	42	0.001	1	1.03	0.042	0.23	<0.1	0.05	1.9	0.3	0.55	3	4.6
726707	Rock	0.132	9	4	1.13	77	0.049	<1	1.75	0.030	0.26	<0.1	0.07	3.6	0.3	1.53	6	4.2
726708	Rock	0.122	26	3	0.40	175	0.001	<1	1.26	0.017	0.19	<0.1	0.27	1.5	0.2	<0.05	4	1.2

QUALITY CONTROL REPORT

SMI08000743.1

Method	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
Unit	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	
MDL	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	
Pulp Duplicates																					
726698	Rock	2.63	24.5	452.1	17.0	50	0.3	3.1	12.3	260	4.28	2.0	0.8	32.2	3.6	26	0.1	0.2	0.4	71	0.53
REP 726698	QC		22.3	459.0	16.5	52	0.3	3.3	12.5	284	4.35	2.3	0.8	31.5	3.9	23	<0.1	0.1	0.4	69	0.53
Reference Materials																					
STD DS7	Standard		16.7	110.0	66.8	376	0.8	55.3	8.8	608	2.33	49.9	4.8	66.4	4.7	72	5.4	5.3	4.3	89	0.91
STD DS7	Standard		19.4	104.7	69.6	370	0.8	55.1	9.6	602	2.38	49.7	5.1	126.4	4.5	73	5.3	5.4	4.4	91	0.93
STD DS7	Standard		19.4	114.9	64.7	393	0.8	56.4	10.7	730	2.62	50.8	4.6	94.6	4.1	68	5.8	5.6	4.3	91	0.87
STD DS7	Standard		20.3	107.3	67.5	378	0.8	56.2	10.0	640	2.37	51.7	4.7	66.5	4.3	71	6.4	6.3	4.5	92	0.91
STD DS7 Expected			20.9	109	70.6	411	0.9	56	9.7	627	2.39	48.2	4.9	70	4.4	69	6.4	5.9	4.5	86	0.93
BLK	Blank		<0.1	0.5	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01
BLK	Blank		<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	10	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01
Prep Wash																					
G1	Prep Blank	<0.01	0.3	7.0	3.7	48	<0.1	4.4	4.3	536	1.88	1.2	2.2	1.9	4.3	60	<0.1	<0.1	<0.1	40	0.50
G1	Prep Blank	<0.01	0.3	3.8	3.2	48	<0.1	4.6	4.5	541	1.75	0.7	2.4	1.6	4.0	51	<0.1	<0.1	<0.1	40	0.45

QUALITY CONTROL REPORT

SMI08000743.1

Method		1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
Analyte		P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se	
Unit		%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
MDL		0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5	
Pulp Duplicates																			
726698	Rock	0.155	7	6	1.04	47	0.063	<1	1.73	0.064	0.19	0.1	0.08	3.3	0.3	0.96	6	3.5	
REP 726698	QC	0.163	6	5	1.06	44	0.058	<1	1.70	0.061	0.17	<0.1	0.09	3.2	0.2	0.98	6	4.2	
Reference Materials																			
STD DS7	Standard	0.070	12	163	0.98	345	0.118	36	0.95	0.069	0.42	3.5	0.17	2.3	4.2	0.18	5	2.9	
STD DS7	Standard	0.071	12	166	1.05	346	0.119	37	0.98	0.074	0.45	3.9	0.20	2.3	4.1	0.18	5	3.2	
STD DS7	Standard	0.069	11	156	1.14	435	0.140	34	1.12	0.081	0.58	3.9	0.18	2.4	4.3	0.18	5	3.7	
STD DS7	Standard	0.067	12	168	1.06	396	0.135	31	1.03	0.076	0.49	4.3	0.18	2.4	4.1	0.18	5	3.8	
STD DS7 Expected		0.08	13	163	1.05	370	0.124	39	0.959	0.073	0.44	3.8	0.2	2.5	4.2	0.21	4.6	3.5	
BLK	Blank	<0.001	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5	
BLK	Blank	<0.001	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5	
Prep Wash																			
G1	Prep Blank	0.070	8	11	0.58	197	0.119	1	1.09	0.058	0.49	<0.1	<0.01	1.8	0.4	<0.05	5	<0.5	
G1	Prep Blank	0.066	6	9	0.58	202	0.116	<1	1.04	0.057	0.50	<0.1	<0.01	1.7	0.4	<0.05	5	<0.5	



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.

Vancouver BC V6C 1Z7 Canada

Submitted By:

Glen Garratt

Receiving Lab:

Canada-Smithers

Received:

August 15, 2008

Report Date:

September 09, 2008

Page:

1 of 2

CERTIFICATE OF ANALYSIS

SMI08000755.1

CLIENT JOB INFORMATION

Project: Zymo
Shipment ID: zy-so-08-09
P.O. Number
Number of Samples: 22

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
DISP-RJT-SOIL Immediate Disposal of Soil Reject

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Mincord Exploration Consultants Ltd.
110 - 325 Howe St.
Vancouver BC V6C 1Z7
Canada

CC: Bob Johnston

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status
SS80	22	Dry at 60C sieve 100g to -80 mesh		
Dry at 60C	22	Dry at 60C		
1DX15	22	1:1:1 Aqua Regia digestion ICP-MS analysis	15	Completed

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only. All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.

110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo

Report Date: September 09, 2008

Page: 2 of 2 Part 1

CERTIFICATE OF ANALYSIS

SMI08000755.1

Method	Analyte	Unit	MDL	1DX15 Mo	1DX15 Cu	1DX15 Pb	1DX15 Zn	1DX15 Ag	1DX15 Ni	1DX15 Co	1DX15 Mn	1DX15 Fe	1DX15 As	1DX15 U	1DX15 Au	1DX15 Th	1DX15 Sr	1DX15 Cd	1DX15 Sb	1DX15 Bi	1DX15 V	1DX15 Ca	1DX15 P
				ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	%
				0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	0.001
L98W	8200 N	Soil		0.7	32.6	56.4	155	2.2	14.2	5.2	570	1.29	8.3	2.4	14.5	0.7	20	0.7	0.7	0.3	30	0.14	0.119
L98W	8250 N	Soil		1.2	18.3	16.4	74	0.2	7.9	3.0	177	2.69	26.1	0.5	23.2	0.5	8	0.2	1.5	0.3	67	<0.01	0.027
L98W	8300 N	Soil		1.3	34.5	41.5	148	0.3	12.5	7.1	819	2.81	38.9	1.0	3.5	0.4	24	0.3	2.0	0.5	46	0.24	0.065
L98W	8350 N	Soil		1.1	42.7	69.0	129	2.9	18.5	5.2	309	2.07	16.3	2.2	9.2	1.2	39	1.0	1.5	0.4	33	0.44	0.152
L98W	8400 N	Soil		1.5	31.4	54.4	141	0.3	11.3	9.0	915	2.76	42.9	0.8	7.5	0.9	12	0.3	1.7	0.6	42	0.06	0.064
L98W	8450 N	Soil		1.5	67.5	51.3	132	0.5	13.2	4.2	235	3.55	33.0	1.2	4.9	0.2	13	0.5	1.8	0.4	76	0.04	0.073
L98W	8500 N	Soil		1.3	56.6	57.9	178	1.4	12.5	6.6	1578	2.97	30.2	1.0	2.2	0.1	28	1.0	1.3	0.4	64	0.53	0.094
L98W	8550 N	Soil		1.7	68.3	157.9	285	0.4	14.6	9.6	2029	4.07	65.0	1.9	4.9	0.3	9	1.1	2.1	0.8	55	0.04	0.136
L98W	8600 N	Soil		1.3	90.2	106.6	117	1.2	14.1	3.4	156	3.02	30.5	2.1	2.2	0.1	18	0.8	1.9	0.4	63	0.03	0.053
L98W	8650 N	Soil		1.8	45.8	52.1	107	1.6	16.1	6.3	615	3.84	34.5	1.9	5.7	0.2	13	0.2	2.2	0.3	69	0.05	0.139
L98W	8700 N	Soil		1.2	29.2	33.3	49	1.5	9.0	2.8	115	2.08	15.9	1.4	2.9	0.1	16	0.2	0.7	0.3	54	0.09	0.123
L98W	8750 N	Soil		1.6	28.7	56.1	185	1.8	11.4	6.9	1395	3.16	36.5	0.6	3.6	0.5	25	0.4	1.4	0.4	58	0.11	0.071
L98W	8800 N	Soil		1.6	27.6	27.6	189	0.2	6.4	3.8	193	3.08	43.8	0.6	12.3	0.8	7	0.2	2.3	0.8	68	0.03	0.040
L98W	8850 N	Soil		0.9	17.0	100.5	135	0.8	5.2	3.9	824	2.51	26.2	0.5	8.9	0.3	6	0.6	1.2	1.0	56	0.02	0.061
L98W	8900 N	Soil		0.7	18.1	42.0	89	0.6	4.5	3.1	197	2.09	28.3	0.5	10.0	0.1	6	0.2	1.4	0.8	54	0.02	0.034
L98W	9000 N	Soil		2.0	62.7	74.0	320	1.1	8.8	3.9	277	3.40	73.9	0.8	9.1	0.1	14	0.3	2.9	2.1	63	0.09	0.080
L98W	9050 N	Soil		2.2	61.6	96.1	132	2.0	10.0	3.5	212	3.75	91.2	1.1	10.7	0.2	10	0.2	4.1	2.4	44	0.03	0.091
L98W	9100 N	Soil		2.3	119.8	111.4	222	1.6	11.0	13.0	1390	3.95	90.7	2.9	15.2	0.5	10	0.4	2.6	2.2	52	0.03	0.068
L98W	9150 N	Soil		2.3	108.7	102.3	151	1.6	7.1	2.9	147	2.68	46.0	1.2	14.4	0.1	11	0.5	1.9	2.5	33	0.04	0.104
L98W	9200 N	Soil		2.3	161.0	125.4	168	3.2	15.2	5.3	161	3.37	56.6	2.0	12.2	0.3	12	0.9	2.1	2.6	44	0.03	0.054
L98W	9250 N	Soil		2.6	54.3	101.6	175	1.2	15.1	7.8	882	4.50	203.2	0.9	41.6	0.4	8	0.7	1.5	3.3	41	0.07	0.166
L98W	9300 N	Soil		1.7	60.7	82.7	118	2.7	9.2	3.0	563	2.34	61.7	1.7	13.2	0.3	9	0.7	1.3	2.6	42	0.06	0.058



AcmeLabs ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
Report Date: September 09, 2008

Page: 2 of 2 **Part** 2

CERTIFICATE OF ANALYSIS

SMI08000755.1

Method	Analyte	Unit	MDL	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
				La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
				ppm	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	
				1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.05	1	0.5	
L98W 8200 N	Soil			15	17	0.15	223	0.002	2	1.98	0.009	0.10	<0.1	0.31	4.6	0.3	0.09	4	0.7
L98W 8250 N	Soil			6	14	0.05	46	0.011	3	0.77	0.003	0.03	0.1	0.07	1.4	0.1	0.05	5	<0.5
L98W 8300 N	Soil			9	11	0.10	238	0.005	2	0.72	0.004	0.09	0.2	0.10	2.5	0.1	<0.05	3	0.5
L98W 8350 N	Soil			40	14	0.18	334	0.004	3	1.21	0.009	0.12	0.1	0.24	5.3	0.2	0.20	2	<0.5
L98W 8400 N	Soil			7	11	0.07	118	0.003	3	0.68	0.006	0.07	<0.1	0.17	2.2	0.2	0.08	2	<0.5
L98W 8450 N	Soil			7	17	0.09	85	0.013	3	0.78	0.004	0.06	0.1	0.07	1.3	0.2	<0.05	6	<0.5
L98W 8500 N	Soil			10	15	0.11	171	0.010	5	0.83	0.005	0.10	<0.1	0.18	1.2	0.2	0.06	5	<0.5
L98W 8550 N	Soil			14	15	0.05	104	0.006	1	0.86	0.005	0.08	0.2	0.08	1.7	0.2	<0.05	4	<0.5
L98W 8600 N	Soil			9	13	0.03	108	0.012	2	0.62	0.004	0.05	0.1	0.06	0.9	<0.1	<0.05	4	<0.5
L98W 8650 N	Soil			8	18	0.12	63	0.008	<1	1.27	0.006	0.06	0.1	0.16	1.1	0.2	0.11	6	0.6
L98W 8700 N	Soil			10	17	0.15	91	0.012	<1	1.40	0.008	0.08	0.1	0.17	1.4	0.2	0.09	8	<0.5
L98W 8750 N	Soil			7	16	0.11	197	0.005	1	1.32	0.005	0.06	<0.1	0.10	1.9	0.2	<0.05	5	<0.5
L98W 8800 N	Soil			9	9	0.04	40	0.008	5	0.54	0.003	0.03	0.2	0.10	1.9	0.3	<0.05	4	<0.5
L98W 8850 N	Soil			10	8	0.03	44	0.007	3	0.56	0.003	0.03	0.2	0.03	0.6	0.3	<0.05	5	<0.5
L98W 8900 N	Soil			11	7	0.03	39	0.005	3	0.41	0.002	0.04	0.2	0.05	0.7	0.3	<0.05	5	<0.5
L98W 9000 N	Soil			9	10	0.03	53	0.006	5	0.39	0.003	0.05	0.2	0.09	0.7	0.2	0.07	5	0.5
L98W 9050 N	Soil			8	8	0.03	64	0.005	3	0.77	0.003	0.04	0.2	0.16	0.9	0.2	0.08	4	0.8
L98W 9100 N	Soil			15	12	0.08	63	0.005	2	1.41	0.004	0.06	0.2	0.12	1.8	0.2	<0.05	4	1.9
L98W 9150 N	Soil			10	5	0.02	74	0.004	5	0.33	0.005	0.05	0.2	0.03	0.3	0.2	0.07	2	<0.5
L98W 9200 N	Soil			18	8	0.02	112	0.005	2	0.40	0.003	0.05	0.2	0.03	0.9	0.1	<0.05	2	0.7
L98W 9250 N	Soil			8	14	0.03	93	0.004	8	0.67	0.005	0.06	0.2	0.14	1.0	0.3	0.09	4	0.8
L98W 9300 N	Soil			15	12	0.07	153	0.003	2	1.00	0.004	0.06	0.1	0.20	0.8	0.3	<0.05	4	<0.5

QUALITY CONTROL REPORT

SMI08000755.1

Method	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	P	
Unit	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	%	
MDL	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	0.001	
Reference Materials																					
STD DS7	Standard	18.9	109.1	68.5	381	0.8	57.0	10.2	715	2.62	48.3	4.5	63.8	3.7	69	5.8	5.8	4.2	92	0.88	0.067
STD DS7	Standard	19.3	114.5	69.6	394	0.8	54.3	10.2	746	2.62	47.8	5.0	91.3	4.5	78	5.8	5.9	4.6	93	0.86	0.073
STD DS7 Expected		20.9	109	70.6	411	0.9	56	9.7	627	2.39	48.2	4.9	70	4.4	69	6.4	5.9	4.5	86	0.93	0.08
BLK	Blank	<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01	<0.001
BLK	Blank	<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01	<0.001

QUALITY CONTROL REPORT

SMI08000755.1

Method	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
Analyte	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se	
Unit	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
MDL	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5	
Reference Materials																	
STD DS7	Standard	12	168	1.14	409	0.138	36	1.05	0.083	0.57	4.0	0.21	2.5	4.2	0.18	5	2.7
STD DS7	Standard	12	166	1.20	450	0.155	36	1.18	0.089	0.62	3.5	0.19	2.9	4.0	0.19	5	3.4
STD DS7 Expected		13	163	1.05	370	0.124	39	0.959	0.073	0.44	3.8	0.2	2.5	4.2	0.21	5	3.5
BLK	Blank	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
BLK	Blank	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.

Vancouver BC V6C 1Z7 Canada

Submitted By:

Glen Garratt

Receiving Lab:

Canada-Smithers

Received:

August 15, 2008

Report Date:

September 02, 2008

Page:

1 of 2

CERTIFICATE OF ANALYSIS

SMI08000757.1

CLIENT JOB INFORMATION

Project: Zymo
Shipment ID: zy-rk-08-12
P.O. Number
Number of Samples: 13

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
DISP-RJT Dispose of Reject After 90 days

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Mincord Exploration Consultants Ltd.
110 - 325 Howe St.
Vancouver BC V6C 1Z7
Canada

CC: Bob Johnston

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status
R150	13	Crush, split and pulverize rock to 200 mesh		
1DX15	13	1:1:1 Aqua Regia digestion ICP-MS analysis	15	Completed

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only. All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
Report Date: September 02, 2008

Page: 2 of 2 **Part** 1

CERTIFICATE OF ANALYSIS

SMI08000757.1

Method	Analyte	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca
Unit		kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%
MDL		0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01
726709	Rock	0.68	1.8	28.1	11.0	63	<0.1	2.3	12.1	1113	4.57	2.8	0.7	0.7	2.6	79	<0.1	0.1	0.4	97	1.18
726710	Rock	1.56	0.2	0.7	13.2	81	<0.1	2.2	3.7	800	1.18	0.8	3.2	<0.5	10.8	140	0.6	0.2	<0.1	8	2.22
726711	Rock	1.68	14.4	717.9	21.0	78	1.3	4.2	10.6	170	3.64	149.8	5.2	52.9	4.0	27	0.2	9.7	5.1	6	0.20
726712	Rock	2.32	15.9	398.1	32.3	21	1.3	1.9	4.5	43	4.19	39.0	3.8	57.7	6.8	6	<0.1	3.2	4.2	5	0.04
726713	Rock	2.03	8.3	436.2	63.5	127	1.2	4.2	12.2	439	4.89	10.0	5.2	26.5	10.0	15	0.7	0.2	3.8	6	0.53
726714	Rock	2.29	5.5	572.8	22.8	137	0.5	3.8	9.1	928	2.87	10.0	6.1	34.0	8.9	32	0.5	0.2	2.9	13	1.35
726715	Rock	2.39	12.4	1065	45.5	174	1.3	3.9	9.9	509	4.31	116.2	4.5	106.1	4.9	25	1.6	1.2	0.9	23	0.40
726716	Rock	2.80	10.0	1486	8.4	70	0.5	3.8	9.4	491	3.74	358.1	3.1	81.6	3.5	58	0.3	1.1	0.3	34	1.66
726717	Rock	1.94	22.0	695.2	6.7	21	0.6	2.8	8.7	132	3.57	3.8	3.5	95.7	8.6	10	<0.1	0.1	0.3	15	0.11
726718	Rock	1.90	0.5	14.6	13.3	114	<0.1	33.4	12.7	1709	1.67	17.2	0.5	3.8	1.4	65	0.8	0.4	<0.1	20	0.62
726719	Rock	2.25	18.7	545.4	78.5	112	0.8	3.4	6.5	383	3.36	25.4	6.0	13.7	10.4	15	0.5	1.1	1.1	17	0.38
726720	Rock	2.82	5.9	268.7	385.0	663	1.7	4.1	11.5	1336	3.51	65.4	6.2	9.5	8.3	42	4.0	4.5	3.7	10	1.86
726721	Rock	2.71	8.9	112.4	66.5	27	0.4	2.1	4.5	225	2.71	4.8	4.5	8.6	9.5	16	<0.1	0.4	1.0	20	0.29



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.

Vancouver BC V6C 1Z7 Canada

Project:

Zymo

Report Date:

September 02, 2008

Page:

2 of 2

Part 2

CERTIFICATE OF ANALYSIS

SMI08000757.1

Method	Analyte	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
		P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
Unit		%	ppm	ppm	%	ppm	%	ppm	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm
MDL		0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.05	1	0.5	
726709	Rock	0.196	13	4	1.17	142	0.112	2	2.35	0.083	0.11	0.3	0.02	4.1	0.1	0.54	10	<0.5
726710	Rock	0.081	20	3	0.08	200	0.001	3	0.41	0.018	0.25	<0.1	0.42	3.0	0.2	<0.05	<1	<0.5
726711	Rock	0.062	6	2	0.07	18	<0.001	2	0.53	0.016	0.31	0.1	0.16	1.1	0.3	3.91	1	3.0
726712	Rock	0.063	18	2	0.04	31	<0.001	<1	0.44	0.011	0.28	0.1	0.13	0.9	0.3	1.94	<1	4.1
726713	Rock	0.118	17	3	0.17	20	0.001	<1	0.58	0.012	0.36	0.1	0.03	0.9	0.3	4.84	1	4.7
726714	Rock	0.128	14	2	0.53	48	0.001	3	0.61	0.014	0.30	0.1	<0.01	1.5	0.2	2.12	1	2.1
726715	Rock	0.139	7	3	0.14	21	0.001	2	0.60	0.010	0.37	0.1	0.97	3.0	0.9	2.41	2	1.8
726716	Rock	0.106	6	3	0.41	89	0.002	4	0.53	0.020	0.25	0.2	0.02	3.8	0.2	0.94	2	1.3
726717	Rock	0.130	11	3	0.13	87	0.002	<1	0.76	0.013	0.45	0.4	0.01	0.8	0.3	1.40	2	2.0
726718	Rock	0.026	4	14	0.19	165	<0.001	2	0.32	0.015	0.14	<0.1	0.10	4.1	<0.1	<0.05	<1	<0.5
726719	Rock	0.194	11	2	0.31	74	0.002	<1	0.80	0.013	0.28	0.1	0.17	1.9	0.4	2.16	2	4.0
726720	Rock	0.166	6	2	0.52	33	0.001	1	0.59	0.012	0.24	<0.1	0.43	1.2	0.4	3.83	1	5.1
726721	Rock	0.184	17	3	0.54	108	0.002	<1	1.00	0.023	0.29	<0.1	0.04	1.4	0.3	1.20	3	3.9

QUALITY CONTROL REPORT

SMI08000757.1

Method	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
Unit	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	
MDL	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	
Reference Materials																					
STD DS7	Standard	20.3	108.3	78.7	401	0.8	54.9	9.5	606	2.34	53.6	5.8	65.6	5.1	74	6.5	6.6	5.2	84	0.92	
STD DS7	Standard	19.4	110.1	75.1	401	0.9	55.9	9.2	633	2.36	50.1	5.3	71.2	4.9	78	6.1	6.6	5.0	84	0.95	
STD DS7 Expected		20.9	109	70.6	411	0.9	56	9.7	627	2.39	48.2	4.9	70	4.4	69	6.4	5.9	4.5	86	0.93	
BLK	Blank	<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01	
Prep Wash																					
G1	Prep Blank	<0.01	0.2	2.2	3.1	46	<0.1	4.2	4.4	559	1.84	<0.5	2.5	<0.5	4.6	63	<0.1	<0.1	<0.1	37	0.47
G1	Prep Blank	<0.01	0.2	2.2	3.0	45	<0.1	4.3	4.4	544	1.84	<0.5	2.6	<0.5	5.2	61	<0.1	<0.1	<0.1	37	0.45

QUALITY CONTROL REPORT

SMI08000757.1

Method		1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte		P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
Unit		%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm
MDL		0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5
Reference Materials																		
STD DS7	Standard	0.080	12	179	1.03	381	0.117	38	0.94	0.074	0.43	4.1	0.19	2.3	4.3	0.19	4	3.8
STD DS7	Standard	0.075	13	171	1.04	403	0.127	40	0.99	0.080	0.44	3.9	0.20	2.4	4.1	0.19	5	3.5
STD DS7 Expected		0.08	13	163	1.05	370	0.124	39	0.959	0.073	0.44	3.8	0.2	2.5	4.2	0.21	4.6	3.5
BLK	Blank	<0.001	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
Prep Wash																		
G1	Prep Blank	0.071	7	10	0.63	229	0.132	1	1.05	0.068	0.53	0.1	<0.01	1.9	0.4	<0.05	5	<0.5
G1	Prep Blank	0.077	7	12	0.60	220	0.127	<1	0.95	0.057	0.52	0.1	<0.01	1.9	0.4	<0.05	4	<0.5



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.

Vancouver BC V6C 1Z7 Canada

Submitted By:

Glen Garratt

Receiving Lab:

Canada-Smithers

Received:

August 18, 2008

Report Date:

September 08, 2008

Page:

1 of 2

CERTIFICATE OF ANALYSIS

SMI08000767.1

CLIENT JOB INFORMATION

Project: Zymo
Shipment ID: zy-rk-08-13
P.O. Number
Number of Samples: 26

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
DISP-RJT Dispose of Reject After 90 days

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Mincord Exploration Consultants Ltd.
110 - 325 Howe St.
Vancouver BC V6C 1Z7
Canada

CC: Bob Johnston

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status
R150	26	Crush, split and pulverize rock to 200 mesh		
1DX15	26	1:1:1 Aqua Regia digestion ICP-MS analysis	15	Completed

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only. All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
 Report Date: September 08, 2008

Page: 2 of 2 Part 1

CERTIFICATE OF ANALYSIS

SMI08000767.1

Method	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
Unit	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	
MDL	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	
726722	Rock	2.02	3.2	24.8	2.7	23	<0.1	5.7	10.6	107	3.72	8.1	1.5	14.0	1.0	25	<0.1	0.1	0.7	8	0.63
726723	Rock	2.25	13.9	1519	13.2	56	1.5	14.3	18.1	294	5.53	7.7	2.6	97.7	0.7	23	0.3	1.1	0.4	266	0.61
726724	Rock	0.97	3.8	1463	5.2	43	1.3	4.9	8.1	314	4.45	1.8	1.5	81.6	2.3	80	0.3	0.2	0.2	162	1.59
726725	Rock	2.01	19.1	30.3	8.3	196	0.2	37.2	4.8	770	2.55	12.6	2.0	<0.5	0.6	12	2.7	1.8	<0.1	64	0.20
726726	Rock	1.54	0.9	17.6	4.2	72	<0.1	5.2	3.2	588	2.79	3.7	0.9	<0.5	0.8	27	0.2	0.4	<0.1	6	0.62
726727	Rock	1.93	9.3	14.9	21.5	165	0.2	9.5	14.7	1004	5.91	36.9	0.7	<0.5	0.4	97	0.4	2.6	0.1	68	2.97
726728	Rock	1.86	0.6	24.7	12.1	57	0.1	10.4	7.3	587	4.18	10.3	0.4	<0.5	0.7	20	0.1	2.2	<0.1	26	0.27
726729	Rock	2.17	0.4	41.4	6.4	65	<0.1	10.3	14.6	1019	5.32	3.7	0.6	10.7	1.1	42	0.2	2.2	1.1	86	1.50
726730	Rock	2.14	1.4	57.9	6.2	47	<0.1	8.9	6.8	440	3.24	1.2	0.4	20.6	1.1	41	0.2	0.6	1.7	48	1.69
726731	Rock	2.21	2.9	220.6	6.1	46	1.2	3.1	5.7	589	14.34	10.4	1.2	5616	0.5	3	0.1	0.4	70.6	70	0.07
726732	Rock	2.75	0.4	603.1	9.6	26	0.6	17.1	12.2	350	21.24	3.2	0.6	273.4	0.5	4	<0.1	1.5	22.0	49	0.17
726733	Rock	2.26	0.7	158.6	5.9	45	0.1	10.7	16.8	699	3.99	20.9	0.9	3.7	1.5	15	0.2	2.1	1.4	28	0.51
726734	Rock	1.96	0.5	34.3	10.0	84	<0.1	12.1	13.6	711	5.40	17.4	0.4	18.5	0.6	24	0.3	0.7	0.5	84	0.73
726735	Rock	2.35	1.3	85.7	11.3	68	<0.1	5.7	11.3	572	4.16	4.7	4.7	2.2	9.4	68	0.4	1.2	1.0	36	1.13
726736	Rock	1.98	6.2	48.7	72.1	74	0.3	0.7	0.7	148	3.41	5.2	2.3	28.0	6.5	10	<0.1	0.3	1.2	<2	0.04
726737	Rock	2.11	2.0	52.2	212.5	385	1.3	3.7	11.7	380	3.97	30.5	5.4	20.2	8.0	13	2.8	0.7	1.2	<2	0.26
726738	Rock	1.59	1.2	12.9	44.1	100	0.3	5.4	11.4	1536	3.07	5.9	5.7	11.7	7.4	52	0.5	0.1	2.0	<2	2.59
726739	Rock	2.35	15.1	865.1	>10000	>10000	25.8	5.3	9.7	4783	5.83	246.1	7.6	273.4	4.1	29	292.3	19.1	7.1	<2	0.99
726740	Rock	2.40	1.2	29.6	132.6	90	0.5	1.2	3.6	128	4.12	10.4	3.0	11.6	7.2	8	0.3	0.6	1.2	9	0.05
726741	Rock	2.69	3.5	170.7	189.6	364	0.6	1.4	14.0	3896	15.50	76.0	3.3	5.8	14.5	8	1.2	2.3	1.8	5	0.10
726742	Rock	1.98	1.1	37.5	86.1	21	0.2	1.8	5.1	29	3.34	14.5	6.2	4.5	8.8	13	<0.1	1.2	0.5	7	0.22
726743	Rock	2.28	1.6	84.7	25.2	83	0.2	4.1	11.6	512	3.16	5.7	3.1	20.2	4.9	66	0.4	<0.1	2.5	30	2.64
726744	Rock	1.53	0.7	32.5	7.3	65	<0.1	3.9	11.4	1069	3.08	9.0	3.4	1.3	6.5	87	0.3	2.9	0.8	41	3.00
726745	Rock	0.73	0.9	24.9	18.7	69	<0.1	11.3	17.3	890	3.02	28.7	0.3	<0.5	0.6	154	0.2	0.7	<0.1	21	4.24
726746	Rock	2.09	3.2	1174	>10000	>10000	>100	0.5	0.9	1045	4.55	568.3	3.1	3366	0.8	18	882.9	425.7	2.4	<2	0.03
830963	Rock	1.00	0.6	25.3	197.4	307	0.7	7.8	13.1	808	4.83	30.4	0.2	7.2	0.7	66	1.2	1.2	0.1	35	1.60



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
 Report Date: September 08, 2008

Page: 2 of 2 Part 2

CERTIFICATE OF ANALYSIS

SMI08000767.1

Method	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se	
Unit	%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
MDL	0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5	
726722	Rock	0.018	4	3	0.49	21	0.002	<1	0.91	0.061	0.23	0.2	0.01	1.0	0.2	3.50	2	2.7
726723	Rock	0.049	2	39	1.10	62	0.192	<1	2.04	0.091	0.22	0.5	0.03	13.2	0.4	2.03	9	1.9
726724	Rock	0.104	7	4	1.11	91	0.195	3	2.20	0.113	0.18	0.1	0.03	2.8	0.2	0.42	8	0.6
726725	Rock	0.061	8	10	0.29	155	0.002	<1	0.92	0.030	0.17	0.1	0.07	3.4	0.2	0.53	3	1.8
726726	Rock	0.041	4	3	0.58	66	0.003	<1	1.17	0.044	0.08	<0.1	0.05	1.6	<0.1	0.30	5	1.3
726727	Rock	0.104	5	13	1.18	53	0.002	<1	2.04	0.023	0.11	<0.1	0.03	5.2	<0.1	2.01	7	1.1
726728	Rock	0.055	8	8	0.52	52	0.001	<1	1.78	0.046	0.14	<0.1	0.01	3.8	<0.1	0.54	4	0.7
726729	Rock	0.083	6	21	1.20	76	0.003	3	1.64	0.032	0.19	<0.1	0.02	7.4	0.2	1.33	6	1.1
726730	Rock	0.043	6	13	0.66	70	0.001	<1	0.98	0.020	0.18	<0.1	<0.01	3.7	0.1	1.02	4	0.6
726731	Rock	0.103	4	13	0.99	27	0.007	<1	1.56	0.006	0.15	0.1	0.02	6.4	0.2	2.16	10	3.4
726732	Rock	0.088	2	9	1.03	6	0.003	1	1.78	0.011	0.10	<0.1	0.05	5.3	0.4	>10	7	4.9
726733	Rock	0.050	7	6	0.42	74	0.001	<1	0.78	0.013	0.25	<0.1	0.02	2.2	0.3	1.45	2	1.2
726734	Rock	0.063	4	18	1.33	201	0.001	1	2.29	0.026	0.17	<0.1	0.07	6.6	0.5	0.34	9	0.6
726735	Rock	0.153	24	3	0.57	175	0.010	<1	0.86	0.030	0.19	0.1	0.03	3.2	0.3	0.64	3	0.9
726736	Rock	0.086	11	1	0.05	107	<0.001	<1	0.44	0.017	0.23	<0.1	0.06	0.6	0.3	0.10	1	6.6
726737	Rock	0.145	13	<1	0.11	23	0.001	1	0.43	0.007	0.27	<0.1	0.05	0.7	0.3	3.20	1	2.5
726738	Rock	0.131	14	2	0.89	26	<0.001	<1	0.39	0.010	0.19	<0.1	<0.01	1.9	0.3	3.17	<1	3.1
726739	Rock	0.096	7	3	0.21	11	<0.001	<1	0.46	0.005	0.15	2.9	1.71	2.6	1.0	7.36	68	11.3
726740	Rock	0.125	13	1	0.05	89	<0.001	<1	0.33	0.008	0.20	<0.1	<0.01	0.5	0.2	0.95	<1	2.8
726741	Rock	0.425	9	2	0.06	68	0.003	<1	0.53	0.007	0.21	0.4	0.08	0.8	0.3	1.35	2	4.9
726742	Rock	0.199	8	2	0.06	57	0.001	<1	0.43	0.024	0.18	<0.1	0.03	0.9	0.3	1.41	1	5.4
726743	Rock	0.130	14	2	0.85	23	<0.001	3	0.38	0.034	0.13	<0.1	0.02	6.0	0.1	2.33	1	0.5
726744	Rock	0.154	20	2	0.81	62	0.001	3	0.39	0.028	0.16	<0.1	0.44	6.5	0.1	0.98	1	<0.5
726745	Rock	0.038	3	4	1.37	365	<0.001	3	0.48	0.009	0.16	<0.1	0.10	7.8	<0.1	0.17	1	<0.5
726746	Rock	0.029	3	<1	0.01	14	<0.001	<1	0.08	0.002	0.09	0.3	17.41	0.4	2.7	9.74	32	21.1
830963	Rock	0.062	6	7	0.74	33	<0.001	3	0.64	0.027	0.19	<0.1	0.12	6.8	<0.1	0.25	2	<0.5

QUALITY CONTROL REPORT

SMI08000767.1

Method	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
Unit	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	
MDL	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	
Pulp Duplicates																					
726732	Rock	2.75	0.4	603.1	9.6	26	0.6	17.1	12.2	350	21.24	3.2	0.6	273.4	0.5	4	<0.1	1.5	22.0	49	0.17
REP 726732	QC		0.2	592.5	10.2	27	0.6	16.8	12.3	350	20.78	4.7	0.6	293.7	0.5	4	<0.1	1.8	23.1	41	0.16
Reference Materials																					
STD DS7	Standard		20.0	117.7	75.0	403	0.8	59.1	10.0	681	2.50	49.8	5.3	62.5	4.8	74	5.5	6.3	4.9	90	0.95
STD DS7	Standard		20.4	128.8	78.6	413	0.8	61.2	10.9	715	2.59	54.0	5.4	62.6	4.8	77	6.5	6.0	4.8	90	0.96
STD DS7 Expected			20.9	109	70.6	411	0.9	56	9.7	627	2.39	48.2	4.9	70	4.4	69	6.4	5.9	4.5	86	0.93
BLK	Blank		<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01
Prep Wash																					
G1	Prep Blank	<0.01	0.9	2.8	3.1	44	<0.1	7.5	4.8	545	1.82	0.6	11.0	<0.5	4.8	52	<0.1	<0.1	<0.1	38	0.43
G1	Prep Blank	<0.01	1.1	3.0	3.1	46	<0.1	6.4	4.8	542	1.87	<0.5	28.9	<0.5	4.9	55	<0.1	<0.1	<0.1	38	0.46

QUALITY CONTROL REPORT

SMI08000767.1

Method		1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte		P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
Unit		%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm
MDL		0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5
Pulp Duplicates																		
726732	Rock	0.088	2	9	1.03	6	0.003	1	1.78	0.011	0.10	<0.1	0.05	5.3	0.4	>10	7	4.9
REP 726732	QC	0.082	2	8	1.04	7	0.001	<1	1.78	0.010	0.11	<0.1	0.05	5.3	0.4	>10	7	6.4
Reference Materials																		
STD DS7	Standard	0.072	12	175	1.08	378	0.129	41	1.03	0.078	0.48	3.9	0.19	2.3	4.4	0.19	5	3.4
STD DS7	Standard	0.073	13	181	1.14	400	0.140	40	1.09	0.084	0.50	3.9	0.23	2.3	4.3	0.19	5	3.9
STD DS7 Expected		0.08	13	163	1.05	370	0.124	39	0.959	0.073	0.44	3.8	0.2	2.5	4.2	0.21	4.6	3.5
BLK	Blank	<0.001	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
Prep Wash																		
G1	Prep Blank	0.073	7	12	0.58	206	0.120	2	0.93	0.055	0.50	0.6	<0.01	1.6	0.4	<0.05	5	0.7
G1	Prep Blank	0.074	7	14	0.60	206	0.123	<1	0.95	0.062	0.50	0.4	<0.01	1.6	0.4	<0.05	4	0.6



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.

Vancouver BC V6C 1Z7 Canada

Submitted By:

Glen Garratt

Receiving Lab:

Canada-Smithers

Received:

August 21, 2008

Report Date:

September 09, 2008

Page:

1 of 3

CERTIFICATE OF ANALYSIS

SMI08000785.1

CLIENT JOB INFORMATION

Project: Zymo
Shipment ID: zy-so-08-11
P.O. Number
Number of Samples: 54

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
DISP-RJT-SOIL Immediate Disposal of Soil Reject

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Mincord Exploration Consultants Ltd.
110 - 325 Howe St.
Vancouver BC V6C 1Z7
Canada

CC: Bob Johnston

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status
SS80	54	Dry at 60C sieve 100g to -80 mesh		
Dry at 60C	54	Dry at 60C		
1DX15	54	1:1:1 Aqua Regia digestion ICP-MS analysis	15	Completed

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only. All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
 Report Date: September 09, 2008

Page: 2 of 3 Part 1

CERTIFICATE OF ANALYSIS

SMI08000785.1

Method	Analyte	Unit	MDL	1DX15 Mo	1DX15 Cu	1DX15 Pb	1DX15 Zn	1DX15 Ag	1DX15 Ni	1DX15 Co	1DX15 Mn	1DX15 Fe	1DX15 As	1DX15 U	1DX15 Au	1DX15 Th	1DX15 Sr	1DX15 Cd	1DX15 Sb	1DX15 Bi	1DX15 V	1DX15 Ca	1DX15 P
				ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	%
				0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	0.001
L104W 83 00N	Soil			1.8	43.4	160.6	205	1.5	13.5	9.8	1197	6.41	76.2	1.1	15.1	2.6	11	0.5	2.8	0.9	79	0.04	0.302
L104W 83 50N	Soil			1.6	47.8	92.3	166	0.6	13.8	14.7	1658	4.60	55.8	1.1	8.5	1.4	15	0.5	2.8	0.6	57	0.08	0.470
L104W 84 00N	Soil			1.6	34.7	39.3	98	0.5	8.3	4.7	385	3.15	35.7	0.7	4.4	0.2	13	<0.1	2.5	0.5	65	0.02	0.135
L104W 84 50N	Soil			1.6	53.2	61.8	167	0.9	13.5	5.9	356	3.64	49.7	1.2	11.5	0.3	24	0.5	2.9	0.6	65	0.20	0.133
L104W 85 00N	Soil			1.4	47.6	54.8	157	0.3	17.7	11.9	882	3.56	41.1	1.0	9.0	1.4	23	0.5	2.8	0.4	62	0.08	0.065
L104W 85 50N	Soil			1.3	40.0	47.3	157	0.3	20.5	13.8	1531	3.22	36.5	1.2	7.2	1.8	41	0.7	2.2	0.3	56	0.31	0.071
L104W 86 00N	Soil			1.6	76.9	107.1	281	3.7	15.8	11.0	1780	4.21	52.9	3.3	17.0	0.7	23	1.3	2.5	1.3	66	0.09	0.116
L104W 86 50N	Soil			1.7	52.7	77.1	230	3.2	16.5	14.6	2534	4.88	43.8	2.1	12.4	0.4	22	1.6	2.0	0.8	83	0.05	0.121
L104W 87 00N	Soil			1.3	45.6	103.9	206	0.3	15.8	14.2	1641	4.77	49.9	1.0	4.3	0.8	15	0.7	2.2	0.9	67	0.05	0.264
L104W 87 50N	Soil			1.8	78.5	224.8	385	0.6	15.4	16.7	2310	5.15	70.7	2.6	38.8	1.8	16	1.3	2.1	1.8	69	0.08	0.142
L104W 88 00N	Soil			1.8	49.8	179.1	260	0.4	13.0	9.3	1118	6.63	73.0	1.2	85.3	0.6	12	0.4	2.7	1.9	78	0.07	0.097
L104W 88 50N	Soil			1.8	67.9	223.4	261	1.3	12.6	8.3	1280	5.64	79.1	1.2	22.0	0.7	13	1.0	2.9	2.5	77	0.06	0.317
L104W 89 00N	Soil			1.9	45.9	83.8	168	0.9	7.1	3.6	267	3.36	48.4	0.8	6.5	0.3	13	0.1	2.6	0.7	72	0.02	0.103
L104W 89 50N	Soil			1.3	53.1	154.1	163	2.8	11.5	8.2	1268	4.04	42.1	2.1	7.3	0.4	13	0.3	2.1	0.9	74	0.04	0.145
L104W 90 00N	Soil			1.7	44.3	136.9	243	0.4	10.7	5.6	747	4.55	68.7	1.6	39.5	0.5	16	0.5	2.3	1.8	86	0.04	0.085
L104W 90 50N	Soil			1.6	43.3	80.9	109	1.7	6.7	5.5	758	3.32	58.9	1.3	152.3	0.4	18	1.0	1.7	1.8	72	0.10	0.036
L104W 91 00N	Soil			1.7	55.6	96.6	177	3.2	6.8	3.0	195	3.15	60.0	0.9	11.6	0.3	9	0.6	2.1	3.0	69	0.02	0.076
L104W 91 50N	Soil			1.5	70.5	177.0	290	1.2	14.5	13.3	2580	4.86	79.0	1.7	13.8	0.7	14	1.2	2.6	3.5	59	0.05	0.156
L104W 92 00N	Soil			1.8	59.2	169.4	250	0.9	11.1	11.5	2513	5.03	72.6	1.0	15.2	0.9	9	0.7	2.6	2.3	62	0.04	0.132
L104W 93 00N	Soil			1.7	67.9	62.2	131	10.9	8.3	3.2	161	2.18	27.8	2.6	118.1	0.3	22	0.4	1.1	1.4	44	0.13	0.073
L108W 87 00N	Soil			1.1	17.0	26.5	123	0.2	9.2	6.7	832	4.21	22.5	0.8	<0.5	1.8	11	0.3	1.4	0.3	81	0.03	0.089
L108W 87 50N	Soil			1.2	22.3	67.9	333	1.0	15.0	8.7	698	3.40	30.9	1.3	6.3	2.7	15	0.6	1.2	0.2	62	0.15	0.108
L108W 88 00N	Soil			3.1	70.0	313.9	400	3.3	11.2	8.9	915	6.72	136.9	2.1	55.3	2.7	9	0.5	4.6	5.1	70	0.05	0.172
L108W 88 50N	Soil			1.4	50.2	143.8	244	0.7	14.3	8.2	658	4.12	53.6	0.9	17.9	1.7	11	0.4	2.3	1.1	62	0.03	0.073
L108W 89 00N	Soil			1.5	36.2	64.9	143	0.8	10.3	6.8	518	5.21	48.3	0.8	3.3	0.7	13	0.5	2.4	0.8	86	0.02	0.109
L108W 89 50N	Soil			1.6	78.0	82.7	267	1.3	14.0	12.9	1488	4.50	34.4	2.3	7.3	2.1	12	1.6	1.9	0.8	76	0.02	0.140
L108W 90 00N	Soil			1.8	43.6	175.2	292	0.6	9.2	8.9	1470	4.24	75.3	0.8	11.4	1.0	8	0.3	2.3	1.6	59	0.03	0.111
L108W 90 50N	Soil			1.6	64.1	112.9	230	0.5	12.2	8.1	832	3.48	58.6	0.9	23.0	0.8	12	0.2	2.9	1.4	56	0.03	0.075
L108W 91 00N	Soil			2.0	50.9	130.2	217	3.1	9.7	9.9	667	4.48	151.7	1.3	11.2	0.3	18	1.5	2.9	0.6	77	0.04	0.069
L108W 91 50N	Soil			2.3	64.4	128.5	382	0.4	16.1	11.3	1024	3.93	169.8	2.3	25.6	0.9	27	1.3	3.8	1.0	67	0.21	0.037

This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.



AcmeLabs ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
Report Date: September 09, 2008

Page: 2 of 3 **Part** 2

CERTIFICATE OF ANALYSIS

SMI08000785.1

Method	Analyte	Unit	MDL	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15		
				La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
				ppm	ppm	%	ppm	%	ppm	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
				1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.01	0.01	0.01	0.05	1	0.5	
L104W 83 00N	Soil			9	18	0.18	83	0.014	3	1.92	0.004	0.04	0.1	0.20	4.1	0.2	<0.05	7	<0.5
L104W 83 50N	Soil			7	17	0.17	160	0.010	2	1.44	0.006	0.07	0.1	0.13	3.1	0.2	<0.05	4	0.6
L104W 84 00N	Soil			6	13	0.06	52	0.009	4	0.74	0.004	0.06	0.1	0.07	1.6	0.1	0.06	4	<0.5
L104W 84 50N	Soil			9	15	0.09	183	0.009	2	0.93	0.005	0.07	0.1	0.09	2.1	0.2	<0.05	4	<0.5
L104W 85 00N	Soil			7	17	0.23	127	0.015	3	1.04	0.006	0.10	0.1	0.08	4.2	0.1	<0.05	3	<0.5
L104W 85 50N	Soil			12	16	0.28	266	0.015	3	1.01	0.013	0.10	0.1	0.12	6.0	0.2	<0.05	3	<0.5
L104W 86 00N	Soil			22	20	0.21	172	0.008	3	1.84	0.009	0.08	0.1	0.24	4.7	0.2	0.06	6	0.9
L104W 86 50N	Soil			15	20	0.21	233	0.009	1	1.74	0.006	0.07	0.2	0.16	2.8	0.2	0.05	8	<0.5
L104W 87 00N	Soil			8	19	0.23	97	0.011	2	1.87	0.004	0.08	0.1	0.12	2.2	0.2	0.06	7	0.6
L104W 87 50N	Soil			15	20	0.24	135	0.012	3	2.50	0.009	0.07	0.1	0.17	3.8	0.4	0.07	6	0.8
L104W 88 00N	Soil			8	18	0.17	86	0.014	2	1.22	0.004	0.06	0.1	0.13	1.8	0.4	0.08	8	<0.5
L104W 88 50N	Soil			9	15	0.13	84	0.017	2	1.24	0.004	0.06	0.2	0.09	1.9	0.4	0.06	8	0.5
L104W 89 00N	Soil			8	13	0.04	55	0.009	9	0.70	0.003	0.08	0.1	0.03	1.0	0.3	0.06	5	<0.5
L104W 89 50N	Soil			12	16	0.14	84	0.013	2	1.26	0.005	0.09	0.1	0.13	2.1	0.2	0.07	6	0.6
L104W 90 00N	Soil			13	12	0.08	98	0.018	2	0.98	0.004	0.06	0.1	0.06	2.1	0.2	<0.05	9	0.5
L104W 90 50N	Soil			17	9	0.04	176	0.008	2	0.67	0.003	0.04	0.1	0.05	1.4	0.2	<0.05	4	<0.5
L104W 91 00N	Soil			11	9	0.04	64	0.009	3	0.61	0.004	0.06	0.1	0.04	1.2	0.3	<0.05	5	<0.5
L104W 91 50N	Soil			14	14	0.20	125	0.009	2	1.29	0.005	0.08	0.1	0.09	2.0	0.2	0.07	5	0.6
L104W 92 00N	Soil			8	14	0.15	108	0.006	1	1.21	0.004	0.05	0.1	0.08	2.0	0.4	<0.05	6	<0.5
L104W 93 00N	Soil			12	12	0.17	169	0.007	1	1.08	0.009	0.05	0.1	0.67	1.4	0.3	<0.05	5	0.6
L108W 87 00N	Soil			6	19	0.19	93	0.012	1	2.45	0.006	0.04	0.2	0.12	3.0	0.2	<0.05	8	0.5
L108W 87 50N	Soil			14	17	0.24	141	0.007	1	2.74	0.010	0.05	0.1	0.19	4.5	0.2	<0.05	6	0.7
L108W 88 00N	Soil			12	13	0.11	56	0.008	3	1.30	0.005	0.06	0.2	0.14	3.4	0.4	0.08	5	0.9
L108W 88 50N	Soil			7	18	0.23	92	0.006	2	1.80	0.006	0.05	0.1	0.10	3.0	0.3	<0.05	5	<0.5
L108W 89 00N	Soil			6	18	0.18	111	0.012	2	1.79	0.005	0.04	0.2	0.11	2.5	0.2	<0.05	7	0.7
L108W 89 50N	Soil			11	22	0.15	191	0.013	2	2.65	0.008	0.07	0.2	0.14	5.1	0.2	<0.05	6	0.6
L108W 90 00N	Soil			10	12	0.13	64	0.005	3	1.28	0.004	0.05	0.1	0.09	2.0	0.4	0.10	5	0.6
L108W 90 50N	Soil			9	15	0.16	56	0.009	3	1.02	0.010	0.09	0.1	0.06	2.9	0.3	<0.05	4	<0.5
L108W 91 00N	Soil			10	17	0.14	128	0.014	2	1.56	0.005	0.05	0.2	0.22	2.6	0.2	<0.05	7	0.8
L108W 91 50N	Soil			12	16	0.21	132	0.012	<1	1.10	0.005	0.05	0.1	0.15	3.7	0.2	<0.05	4	0.8

This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
 Report Date: September 09, 2008

Page: 3 of 3 Part 1

CERTIFICATE OF ANALYSIS

SMI08000785.1

Method	Analyte	Unit	MDL	1DX15 Mo	1DX15 Cu	1DX15 Pb	1DX15 Zn	1DX15 Ag	1DX15 Ni	1DX15 Co	1DX15 Mn	1DX15 Fe	1DX15 As	1DX15 U	1DX15 Au	1DX15 Th	1DX15 Sr	1DX15 Cd	1DX15 Sb	1DX15 Bi	1DX15 V	1DX15 Ca	1DX15 P
				ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	%
				0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	0.001
L108W 92 00N	Soil			1.2	46.4	183.1	674	0.8	11.8	14.6	2502	4.08	49.9	2.0	74.6	0.6	31	1.7	2.1	1.0	59	0.37	0.114
L108W 92 50N	Soil			1.6	28.1	36.3	134	0.3	6.3	3.9	204	3.42	46.7	0.6	8.4	0.5	10	0.2	2.4	0.9	89	0.02	0.048
L108W 93 00N	Soil			1.4	25.6	54.9	114	0.3	6.7	5.3	642	4.42	32.0	0.5	6.9	0.6	7	0.2	2.4	0.9	80	0.02	0.104
L112W 81 50N	Soil			2.0	43.9	66.4	187	0.8	12.3	5.3	222	6.83	55.1	1.0	8.0	2.7	13	0.4	2.0	1.0	68	0.03	0.064
L112W 82 00N	Soil			1.8	12.9	14.4	62	0.4	4.4	2.8	128	2.25	38.9	0.5	3.3	1.0	7	0.2	2.7	0.4	71	0.01	0.026
L112W 82 50N	Soil			2.9	68.0	206.0	232	0.4	9.9	11.8	3830	6.43	218.2	1.6	17.6	0.6	17	0.7	5.1	2.8	55	0.05	0.413
L112W 83 00N	Soil			3.0	68.7	108.5	362	0.9	11.3	13.8	9012	4.88	51.7	1.8	13.0	1.4	16	3.1	2.6	0.9	56	0.09	0.229
L112W 83 50N	Soil			3.3	21.4	58.1	175	0.4	5.6	6.8	621	4.27	27.6	0.3	4.7	0.9	4	0.4	6.5	0.2	39	0.01	0.102
L112W 84 00N	Soil			7.8	15.5	38.4	135	0.4	3.7	5.9	434	3.96	30.6	0.2	1.7	0.5	4	0.2	6.8	0.1	31	0.02	0.097
L112W 84 50N	Soil			1.9	14.8	71.4	194	0.3	2.8	5.8	778	5.83	17.7	0.2	<0.5	0.7	10	0.3	2.7	0.2	48	0.18	0.101
L112W 85 50N	Soil			2.2	22.9	50.3	170	0.2	10.6	5.3	268	5.54	37.4	0.9	2.2	2.0	10	0.2	2.0	0.5	81	0.03	0.083
L112W 86 00N	Soil			1.5	21.4	64.6	177	0.2	8.1	6.5	426	4.47	61.7	0.8	8.8	2.5	8	0.2	1.8	0.5	68	0.02	0.087
L112W 86 50N	Soil			1.6	34.7	42.2	163	0.4	14.0	8.6	746	3.49	37.0	0.9	6.6	1.6	12	0.3	1.8	0.4	66	0.03	0.082
L112W 87 50N	Soil			2.8	63.9	230.6	233	3.8	11.9	27.0	5467	3.95	68.3	3.3	12.0	1.5	24	1.4	2.5	0.8	39	0.16	0.217
L112W 88 00N	Soil			1.4	42.9	54.7	130	0.5	7.8	3.7	321	3.65	44.3	0.8	2.0	0.3	12	0.4	2.3	1.0	89	0.02	0.075
L112W 88 50N	Soil			1.6	40.8	70.2	254	0.6	13.8	10.0	2451	3.58	50.2	1.4	15.9	0.6	45	1.2	2.1	0.8	64	0.31	0.093
L112W 89 00N	Soil			1.4	34.6	37.3	210	0.1	13.6	7.1	504	4.22	61.2	1.2	2.4	0.5	54	0.5	2.2	0.4	84	0.35	0.058
L112W 90 00N	Soil			1.3	40.3	47.7	103	0.3	8.6	4.4	260	4.16	40.9	0.9	3.2	0.4	13	0.1	2.3	0.5	84	0.05	0.064
L112W 90 50N	Soil			1.7	25.3	38.4	108	0.1	5.9	4.4	320	3.65	58.9	0.6	7.5	0.4	8	0.4	2.5	0.7	78	0.03	0.025
L112W 91 00N	Soil			3.5	32.4	112.2	430	1.3	7.5	9.0	936	7.79	399.5	0.4	138.3	0.9	7	0.7	7.5	5.6	45	0.02	0.116
L112W 91 50N	Soil			1.2	38.1	111.1	283	0.4	13.1	7.2	586	4.21	70.3	0.8	16.0	2.2	12	0.4	2.8	1.4	61	0.04	0.193
L112W 92 00N	Soil			1.3	47.7	110.6	177	0.2	11.2	5.4	382	4.62	84.1	0.7	16.3	0.6	11	0.6	3.0	1.2	58	0.04	0.071
L112W 92 50N	Soil			1.6	107.0	135.6	375	1.6	22.3	13.8	2367	4.56	71.8	1.9	16.0	1.1	30	1.1	3.0	0.9	76	0.34	0.097
L112W 93 00N	Soil			1.4	26.1	52.1	133	0.3	7.6	5.7	620	3.93	104.1	0.5	3.6	0.3	11	0.3	5.0	1.3	73	0.02	0.046



AcmeLabs ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
Report Date: September 09, 2008

Page: 3 of 3 **Part** 2

CERTIFICATE OF ANALYSIS

SMI08000785.1

Method	Analyte	Unit	MDL	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15		
				La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
				ppm	ppm	%	ppm	%	%	ppm	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
				1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.05	1	0.5	
L108W 92 00N	Soil			14	15	0.20	248	0.012	1	1.44	0.006	0.05	0.1	0.10	2.3	0.1	<0.05	6	<0.5
L108W 92 50N	Soil			8	12	0.07	66	0.016	3	0.90	0.003	0.04	0.1	0.05	2.3	0.3	<0.05	6	<0.5
L108W 93 00N	Soil			7	12	0.09	39	0.024	3	0.86	0.003	0.04	0.2	0.05	2.1	0.2	<0.05	9	<0.5
L112W 81 50N	Soil			6	22	0.20	81	0.009	3	2.40	0.006	0.05	0.1	0.21	3.7	0.2	<0.05	7	0.7
L112W 82 00N	Soil			6	8	0.04	36	0.008	2	0.67	0.005	0.03	0.2	0.05	1.7	0.1	<0.05	6	<0.5
L112W 82 50N	Soil			26	14	0.12	90	0.010	1	1.40	0.005	0.07	0.2	0.10	2.7	0.3	<0.05	5	0.9
L112W 83 00N	Soil			18	15	0.14	294	0.013	2	2.58	0.007	0.06	0.2	0.28	5.2	0.4	<0.05	6	1.0
L112W 83 50N	Soil			9	7	0.07	39	0.003	3	1.04	0.004	0.05	0.2	0.09	3.8	0.2	<0.05	6	<0.5
L112W 84 00N	Soil			5	4	0.05	36	0.001	1	1.15	0.003	0.05	0.3	0.12	4.0	0.3	<0.05	5	<0.5
L112W 84 50N	Soil			5	7	0.15	78	0.001	<1	2.20	0.004	0.05	0.3	0.11	3.9	0.2	<0.05	8	<0.5
L112W 85 50N	Soil			6	20	0.19	78	0.008	2	2.47	0.005	0.05	0.2	0.11	3.4	0.2	<0.05	10	<0.5
L112W 86 00N	Soil			6	17	0.15	79	0.009	1	2.72	0.009	0.04	0.2	0.11	3.4	0.2	<0.05	8	0.5
L112W 86 50N	Soil			7	18	0.23	95	0.006	1	2.15	0.007	0.05	0.1	0.12	3.1	0.2	<0.05	5	<0.5
L112W 87 50N	Soil			19	16	0.10	107	0.006	<1	2.32	0.006	0.04	0.2	0.52	3.8	0.3	0.11	4	1.6
L112W 88 00N	Soil			8	12	0.06	76	0.020	2	0.59	0.003	0.04	0.1	0.04	1.5	0.2	<0.05	8	<0.5
L112W 88 50N	Soil			11	15	0.22	177	0.010	2	1.52	0.007	0.07	0.1	0.10	3.4	0.2	<0.05	5	0.5
L112W 89 00N	Soil			10	20	0.31	179	0.010	2	1.84	0.007	0.08	0.2	0.06	3.4	0.2	<0.05	9	<0.5
L112W 90 00N	Soil			7	17	0.10	88	0.021	3	1.05	0.004	0.07	0.1	0.10	2.0	0.1	<0.05	7	<0.5
L112W 90 50N	Soil			9	10	0.05	44	0.014	3	0.55	0.003	0.04	0.1	0.03	1.6	0.2	<0.05	6	<0.5
L112W 91 00N	Soil			8	9	0.10	77	0.004	1	1.62	0.003	0.06	0.2	0.10	3.4	0.3	<0.05	5	<0.5
L112W 91 50N	Soil			7	17	0.24	90	0.006	<1	2.43	0.005	0.05	0.1	0.16	3.1	0.3	<0.05	6	<0.5
L112W 92 00N	Soil			6	15	0.17	69	0.007	1	1.46	0.004	0.06	0.1	0.16	2.1	0.2	<0.05	5	<0.5
L112W 92 50N	Soil			10	24	0.44	224	0.006	3	2.90	0.008	0.13	0.1	0.12	3.8	0.5	<0.05	9	0.8
L112W 93 00N	Soil			6	13	0.09	60	0.007	4	0.96	0.004	0.07	0.1	0.05	1.9	0.5	<0.05	6	0.7

QUALITY CONTROL REPORT

SMI08000785.1

Method	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
Analyte	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	P	
Unit	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	%	
MDL	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	0.001	
Pulp Duplicates																					
L104W 88 50N	Soil	1.8	67.9	223.4	261	1.3	12.6	8.3	1280	5.64	79.1	1.2	22.0	0.7	13	1.0	2.9	2.5	77	0.06	0.317
REP L104W 88 50N	QC	1.7	65.6	223.5	267	1.3	11.9	8.4	1349	5.49	80.4	1.2	15.6	0.8	12	1.0	2.9	2.6	78	0.06	0.306
L108W 91 00N	Soil	2.0	50.9	130.2	217	3.1	9.7	9.9	667	4.48	151.7	1.3	11.2	0.3	18	1.5	2.9	0.6	77	0.04	0.069
REP L108W 91 00N	QC	1.8	50.9	131.1	223	3.3	9.8	9.7	649	4.54	157.7	1.3	12.3	0.5	18	1.5	3.0	0.7	76	0.04	0.071
L112W 90 50N	Soil	1.7	25.3	38.4	108	0.1	5.9	4.4	320	3.65	58.9	0.6	7.5	0.4	8	0.4	2.5	0.7	78	0.03	0.025
REP L112W 90 50N	QC	1.5	25.1	36.5	112	0.1	6.1	4.6	332	3.73	58.9	0.5	12.8	0.3	8	0.4	2.2	0.7	78	0.04	0.028
Reference Materials																					
STD DS7	Standard	18.1	97.9	66.4	359	0.7	46.4	8.8	611	2.21	45.2	4.7	83.7	4.7	73	5.3	5.7	4.1	82	0.91	0.066
STD DS7	Standard	19.1	107.4	68.8	390	0.9	55.1	9.5	607	2.36	51.1	5.2	67.5	4.8	71	6.9	6.3	4.6	86	0.89	0.076
STD DS7	Standard	19.6	114.8	66.8	399	0.8	55.4	9.6	649	2.40	54.5	5.4	69.8	4.8	75	6.7	6.5	4.6	91	0.95	0.079
STD DS7 Expected		20.9	109	70.6	411	0.9	56	9.7	627	2.39	48.2	4.9	70	4.4	69	6.4	5.9	4.5	86	0.93	0.08
BLK	Blank	<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01	<0.001
BLK	Blank	<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01	<0.001
BLK	Blank	<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01	<0.001

QUALITY CONTROL REPORT

SMI08000785.1

Method	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se	
Unit	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
MDL	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5	
Pulp Duplicates																	
L104W 88 50N	Soil	9	15	0.13	84	0.017	2	1.24	0.004	0.06	0.2	0.09	1.9	0.4	0.06	8	0.5
REP L104W 88 50N	QC	9	14	0.12	83	0.011	1	1.12	0.005	0.05	0.1	0.09	1.9	0.4	0.06	9	<0.5
L108W 91 00N	Soil	10	17	0.14	128	0.014	2	1.56	0.005	0.05	0.2	0.22	2.6	0.2	<0.05	7	0.8
REP L108W 91 00N	QC	10	16	0.15	134	0.012	2	1.60	0.005	0.05	0.2	0.21	2.5	0.2	0.07	7	0.7
L112W 90 50N	Soil	9	10	0.05	44	0.014	3	0.55	0.003	0.04	0.1	0.03	1.6	0.2	<0.05	6	<0.5
REP L112W 90 50N	QC	9	10	0.05	45	0.013	3	0.60	0.004	0.05	0.2	0.02	1.8	0.2	<0.05	6	<0.5
Reference Materials																	
STD DS7	Standard	14	164	0.99	350	0.133	36	1.03	0.084	0.45	4.1	0.16	2.8	4.3	0.19	5	3.7
STD DS7	Standard	13	148	0.99	359	0.122	38	0.98	0.090	0.47	3.9	0.20	3.1	4.2	0.17	5	3.5
STD DS7	Standard	14	157	1.08	396	0.133	35	1.05	0.088	0.50	4.0	0.19	2.9	4.2	0.20	5	3.1
STD DS7 Expected		13	163	1.05	370	0.124	39	0.959	0.073	0.44	3.8	0.2	2.5	4.2	0.21	5	3.5
BLK	Blank	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
BLK	Blank	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
BLK	Blank	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5

CERTIFICATE OF ANALYSIS

SMI08000792.1

CLIENT JOB INFORMATION

Project: Zymo
 Shipment ID: zy-so-08-12
 P.O. Number
 Number of Samples: 74

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
 DISP-RJT-SOIL Immediate Disposal of Soil Reject

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7
 Canada

CC: Bob Johnston

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status
SS80	74	Dry at 60C sieve 100g to -80 mesh		
Dry at 60C	74	Dry at 60C		
1DX15	74	1:1:1 Aqua Regia digestion ICP-MS analysis	15	Completed

ADDITIONAL COMMENTS



CERTIFICATE OF ANALYSIS

SMI08000792.1

Method	Analyte	Unit	MDL	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15		
				Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	P
				ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	%		
				0.1	0.1	0.1	1	0.1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.001		
L112W 87 00N	Soil			5.0	83.3	140.5	218	0.5	6.1	12.4	1923	4.48	94.6	0.7	27.4	0.7	8	1.2	6.5	0.6	44	0.03	0.087
L158W 83 00N	Soil			3.4	72.6	37.7	140	0.2	15.2	13.8	1357	5.39	44.3	1.3	9.1	0.3	10	0.2	1.8	0.6	63	0.06	0.081
L158W 83 50N	Soil			5.1	53.8	55.4	77	1.1	6.1	6.1	626	7.19	67.4	0.7	12.3	2.2	5	0.3	1.7	1.0	94	0.03	0.266
L158W 84 00N	Soil			4.4	81.8	78.1	99	1.3	9.1	6.3	438	6.44	62.6	0.9	17.8	2.3	7	0.4	2.3	0.9	61	0.03	0.103
L158W 84 50N	Soil			4.6	58.1	43.9	84	0.5	6.4	4.4	353	5.04	61.0	0.6	115.2	1.4	7	0.2	1.9	1.1	70	0.02	0.068
L158W 85 00N	Soil			5.3	118.4	95.2	141	1.3	10.5	10.5	594	6.86	76.3	1.0	28.0	3.3	6	0.5	2.1	1.3	53	0.04	0.118
L158W 85 50N	Soil			4.8	185.8	75.8	171	0.4	11.4	9.9	414	4.48	55.2	1.2	31.8	2.9	9	0.3	2.0	0.8	48	0.07	0.097
L158W 86 00N	Soil			5.6	124.4	46.3	118	0.7	9.9	9.8	924	4.63	64.0	0.6	43.1	1.3	6	0.3	1.9	0.8	67	0.02	0.066
L158W 86 50N	Soil			6.3	226.6	69.5	194	0.6	18.8	15.0	881	5.68	104.6	0.9	65.5	3.1	6	0.4	2.2	0.9	56	0.04	0.114
L158W 87 00N	Soil			6.1	133.2	76.1	196	0.5	9.0	9.3	990	5.74	100.4	0.8	30.7	1.5	9	0.5	2.3	1.2	64	0.06	0.137
L158W 87 50N	Soil			5.2	94.3	67.7	138	1.2	12.9	11.6	996	5.34	72.2	0.8	26.3	1.6	9	0.5	2.0	0.9	64	0.04	0.078
L158W 88 00N	Soil			2.7	57.9	44.1	100	0.2	9.0	5.7	366	5.68	52.8	0.5	7.9	1.4	8	0.2	2.2	0.7	75	0.02	0.042
L158W 88 50N	Soil			5.8	126.0	46.4	109	0.8	11.5	8.6	520	4.75	74.0	1.3	19.0	1.1	13	0.3	2.0	0.8	59	0.11	0.081
L158W 89 00N	Soil			3.9	102.6	54.8	110	1.3	10.8	17.5	2643	3.73	51.8	1.2	14.1	0.7	23	0.5	1.4	0.6	48	0.20	0.143
L158W 89 50N	Soil			5.0	56.6	64.0	58	0.5	5.9	6.4	529	8.51	88.2	0.7	194.0	1.2	7	0.3	2.2	0.7	82	0.04	0.091
L158W 90 00N	Soil			6.1	135.3	62.8	93	0.3	13.0	9.9	443	7.02	116.5	0.7	26.4	1.8	5	0.3	2.4	0.9	65	0.02	0.042
L158W 90 50N	Soil			3.1	138.4	83.0	172	0.4	13.6	13.9	1230	4.72	84.3	0.8	17.9	1.5	21	0.3	3.0	0.9	55	0.21	0.137
L158W 91 00N	Soil			3.9	128.8	92.1	187	0.8	11.1	10.1	735	6.21	87.5	0.8	19.8	2.0	10	0.3	2.6	1.3	64	0.05	0.151
L158W 91 50N	Soil			3.9	85.2	30.5	97	0.3	8.4	8.5	768	5.70	78.3	0.7	32.2	0.5	17	0.4	2.1	1.0	66	0.16	0.091
L158W 92 00N	Soil			2.2	51.3	52.1	95	0.2	11.7	6.8	403	5.96	65.3	0.7	8.4	0.7	14	0.9	2.2	0.9	68	0.11	0.060
L158W 92 50N	Soil			2.5	57.3	39.4	81	0.4	10.6	10.7	621	4.87	56.2	0.6	12.2	0.9	10	0.4	1.9	1.0	59	0.10	0.075
L158W 93 00N	Soil			2.1	43.4	37.9	79	0.3	18.5	7.5	356	4.85	22.4	1.1	2.1	0.3	13	0.3	0.8	0.2	74	0.09	0.062
L158W 93 50N	Soil			5.0	102.8	32.5	98	0.6	9.3	12.3	749	4.09	37.9	1.0	25.4	0.6	15	0.3	1.8	0.7	55	0.17	0.112
L158W 94 00N	Soil			2.0	40.2	41.6	85	0.3	9.2	8.7	833	4.44	26.3	1.2	7.8	0.2	13	0.3	0.9	0.3	65	0.10	0.075
L158W 94 50N	Soil			5.3	57.4	67.3	121	0.2	9.2	7.9	697	4.77	96.7	1.0	14.1	0.4	16	0.2	1.9	1.4	78	0.14	0.077
L158W 95 00N	Soil			2.7	49.8	21.8	83	0.2	8.8	11.2	510	4.30	29.1	0.5	4.3	0.8	20	0.2	1.1	0.3	56	0.34	0.067
L158W 95 50N	Soil			3.1	69.9	43.9	220	0.1	18.8	16.4	1273	4.44	35.6	1.1	9.1	0.8	18	0.2	1.6	0.4	57	0.21	0.103
L158W 96 00N	Soil			1.6	30.1	16.4	27	0.3	4.0	2.3	187	3.29	13.4	0.6	1.6	0.1	7	0.3	0.6	0.3	83	0.03	0.042
L158W 96 50N	Soil			4.3	95.7	39.4	101	0.3	11.5	6.3	301	5.22	45.1	1.2	7.7	1.1	9	0.2	1.7	0.7	64	0.06	0.134
L158W 97 00N	Soil			4.8	25.6	29.7	46	<0.1	5.0	3.0	133	3.99	25.5	0.6	4.2	0.1	12	<0.1	1.0	0.5	84	0.13	0.046



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
 Report Date: September 08, 2008

Page: 2 of 4 Part 2

CERTIFICATE OF ANALYSIS

SMI08000792.1

Method	Analyte	Unit	MDL	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
				La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
				ppm	ppm	%	ppm	%	ppm	%	ppm	%	ppm	ppm	ppm	ppm	%	ppm	ppm
				1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.01	0.1	0.01	0.1	0.05	1	0.05
L112W 87 00N	Soil			8	9	0.05	71	0.004	5	1.34	0.005	0.05	0.2	0.17	2.6	0.3	0.06	4	0.9
L158W 83 00N	Soil			6	16	0.36	90	0.012	3	1.78	0.006	0.06	0.1	0.14	2.5	0.1	0.06	7	1.4
L158W 83 50N	Soil			6	17	0.18	42	0.012	1	2.21	0.004	0.04	0.2	0.14	2.7	0.3	<0.05	11	1.1
L158W 84 00N	Soil			6	17	0.22	51	0.006	2	2.15	0.006	0.05	0.2	0.17	3.0	0.2	<0.05	7	1.5
L158W 84 50N	Soil			6	12	0.13	52	0.007	2	1.34	0.005	0.06	0.1	0.14	2.5	0.3	<0.05	6	0.7
L158W 85 00N	Soil			6	17	0.20	51	0.008	1	3.29	0.004	0.03	0.1	0.23	3.5	0.2	<0.05	5	2.3
L158W 85 50N	Soil			9	15	0.25	52	0.007	3	3.16	0.006	0.04	<0.1	0.25	4.7	0.2	<0.05	4	2.5
L158W 86 00N	Soil			6	14	0.18	63	0.006	3	1.79	0.004	0.05	<0.1	0.13	3.0	0.4	<0.05	7	1.2
L158W 86 50N	Soil			8	19	0.35	93	0.004	2	3.29	0.006	0.10	<0.1	0.31	5.2	0.3	<0.05	6	2.3
L158W 87 00N	Soil			8	14	0.20	77	0.009	1	2.12	0.006	0.05	0.1	0.13	3.7	0.4	<0.05	6	1.7
L158W 87 50N	Soil			7	17	0.28	67	0.008	2	1.98	0.006	0.07	0.1	0.17	3.2	0.3	0.06	7	1.1
L158W 88 00N	Soil			6	18	0.21	45	0.008	2	2.17	0.005	0.05	0.1	0.10	3.0	0.3	<0.05	8	0.9
L158W 88 50N	Soil			11	15	0.26	101	0.004	1	1.99	0.006	0.06	0.1	0.17	3.2	0.3	<0.05	6	2.1
L158W 89 00N	Soil			17	12	0.22	173	0.005	1	2.23	0.006	0.07	<0.1	0.14	2.6	0.3	0.06	6	1.8
L158W 89 50N	Soil			6	15	0.19	70	0.011	2	1.88	0.005	0.05	0.2	0.10	2.7	0.3	<0.05	11	1.4
L158W 90 00N	Soil			7	17	0.36	61	0.005	1	2.43	0.007	0.07	<0.1	0.13	4.1	0.3	0.06	7	2.2
L158W 90 50N	Soil			9	13	0.33	112	0.005	2	1.30	0.012	0.11	<0.1	0.10	3.7	0.2	0.19	4	1.9
L158W 91 00N	Soil			7	14	0.26	69	0.005	1	1.93	0.006	0.06	<0.1	0.14	3.8	0.3	<0.05	5	1.2
L158W 91 50N	Soil			9	12	0.19	151	0.006	1	1.64	0.008	0.06	0.1	0.07	2.4	0.2	<0.05	7	1.4
L158W 92 00N	Soil			7	18	0.25	77	0.010	2	2.08	0.008	0.08	<0.1	0.09	2.7	0.3	<0.05	8	0.6
L158W 92 50N	Soil			8	12	0.31	72	0.003	<1	1.68	0.009	0.06	<0.1	0.08	3.3	0.1	<0.05	6	1.2
L158W 93 00N	Soil			8	24	0.38	86	0.016	2	2.26	0.007	0.09	0.9	0.08	2.7	0.2	<0.05	10	0.9
L158W 93 50N	Soil			12	13	0.32	98	0.007	2	1.88	0.009	0.08	0.1	0.09	2.5	0.3	<0.05	7	1.3
L158W 94 00N	Soil			8	14	0.32	64	0.014	<1	2.22	0.011	0.07	<0.1	0.09	2.1	0.2	<0.05	9	1.2
L158W 94 50N	Soil			9	13	0.26	81	0.011	1	1.80	0.008	0.10	0.1	0.07	2.7	0.2	<0.05	8	1.4
L158W 95 00N	Soil			9	11	0.38	130	0.002	<1	1.95	0.009	0.06	<0.1	0.06	3.9	<0.1	<0.05	8	0.8
L158W 95 50N	Soil			15	18	0.37	84	0.007	1	2.36	0.008	0.08	0.2	0.10	4.5	0.2	<0.05	6	1.5
L158W 96 00N	Soil			7	10	0.11	67	0.015	1	1.46	0.009	0.07	0.1	0.05	1.5	0.2	<0.05	10	1.0
L158W 96 50N	Soil			9	16	0.35	69	0.005	2	2.56	0.008	0.10	<0.1	0.12	3.6	0.2	0.06	7	1.2
L158W 97 00N	Soil			7	12	0.15	38	0.014	1	1.85	0.006	0.06	0.2	0.05	1.5	0.2	<0.05	10	0.9

This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

ACME ANALYTICAL LABORATORIES LTD.

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.
Vancouver BC V6C 1Z7 Canada

Project:

Zymo

Report Date:

September 08, 2008

Page:

3 of 4

Part 1

CERTIFICATE OF ANALYSIS

SMI08000792.1

Method Analyte Unit MDL	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
	Mo ppm 0.1	Cu ppm 0.1	Pb ppm 0.1	Zn ppm 1	Ag ppm 0.1	Ni ppm 0.1	Co ppm 0.1	Mn ppm 1	Fe % 0.01	As ppm 0.5	U ppm 0.1	Au ppb 0.5	Th ppm 0.1	Sr ppm 1	Cd ppm 0.1	Sb ppm 0.1	Bi ppm 0.1	V ppm 2	Ca % 0.01	P % 0.001	
L158W 97 50N	Soil	2.1	24.3	17.1	26	0.6	2.3	2.1	221	1.35	15.1	0.6	7.0	0.3	8	0.2	0.5	0.5	37	0.05	0.082
L158W 98 00N	Soil	6.7	23.8	27.4	63	0.2	4.0	6.0	3670	3.54	33.9	0.7	11.8	0.1	13	0.1	0.8	0.5	51	0.23	0.150
L158W 98 50N	Soil	4.5	55.1	46.7	73	0.1	5.9	4.0	261	4.78	55.6	0.8	12.2	0.4	10	0.4	1.5	1.0	85	0.03	0.064
L158W 99 00N	Soil	8.9	91.5	43.6	75	0.3	8.4	4.4	271	5.23	47.4	0.7	11.2	1.0	9	0.3	1.7	0.7	69	0.03	0.095
L158W 100 00N	Soil	5.0	48.0	16.6	94	<0.1	14.4	18.0	468	4.64	17.7	0.7	2.7	0.9	58	0.1	0.7	0.2	81	0.64	0.046
ZSP-08 75	Soil	1.3	12.6	21.7	46	0.3	4.7	2.7	175	3.78	23.0	0.4	1.0	1.2	6	0.1	2.0	0.3	84	0.02	0.041
ZSP-08 76	Soil	1.3	14.9	10.9	44	<0.1	2.3	1.9	61	1.68	1.8	1.4	0.6	2.7	8	0.1	0.2	<0.1	40	0.02	0.046
ZSP-08 77	Soil	1.5	13.4	14.5	32	<0.1	3.2	1.7	67	1.73	3.0	1.0	<0.5	2.7	6	<0.1	0.3	<0.1	46	0.02	0.039
ZSP-08 78	Soil	2.2	14.9	32.9	99	<0.1	9.5	4.9	246	5.48	13.3	2.1	1.0	7.5	8	0.1	0.8	0.3	73	0.03	0.326
ZSP-08 79	Soil	1.4	11.5	8.8	32	0.1	2.6	2.2	75	1.87	2.9	1.4	<0.5	2.0	5	<0.1	0.3	<0.1	53	<0.01	0.028
ZSP-08 80	Soil	0.7	15.5	12.4	41	0.1	3.4	2.5	613	2.58	7.6	1.1	<0.5	1.8	5	0.1	0.6	0.2	65	0.02	0.100
ZSP-08 81	Soil	1.3	10.2	22.5	64	<0.1	4.9	2.8	165	3.77	12.7	1.3	2.6	3.2	7	0.2	0.5	0.2	56	0.02	0.315
ZSP-08 82	Soil	0.6	11.0	8.7	34	<0.1	3.5	1.8	105	1.89	6.4	0.7	<0.5	0.4	7	<0.1	0.6	0.1	47	0.01	0.056
ZSP-08 83	Soil	1.0	13.8	11.9	44	0.1	3.8	2.2	114	2.38	12.0	0.8	1.9	1.1	6	<0.1	0.6	0.2	57	0.01	0.047
ZSP-08 84	Soil	1.0	13.9	18.7	68	0.1	6.7	5.3	245	3.06	12.3	1.2	<0.5	2.8	16	0.1	0.6	0.2	51	0.06	0.104
ZSP-08 85	Soil	1.4	25.2	20.6	67	0.1	8.5	5.0	416	3.44	17.3	2.0	7.4	0.3	31	0.2	1.2	0.3	72	0.16	0.047
ZSP-08 86	Soil	1.3	35.2	20.5	70	0.5	7.9	4.4	223	3.37	15.9	1.8	3.4	0.3	17	0.3	1.0	0.3	76	0.04	0.078
ZSP-08 87	Soil	1.2	23.6	13.7	123	0.3	15.5	7.2	342	2.89	17.3	2.0	54.7	1.1	17	0.1	0.7	0.3	61	0.06	0.080
ZSP-08 88	Soil	1.6	23.9	22.4	113	0.5	17.3	9.8	553	3.07	19.2	6.0	1.6	0.9	34	0.3	0.9	0.3	56	0.15	0.106
ZSP-08 89	Soil	1.3	13.9	14.2	69	0.1	6.2	3.6	230	2.93	15.8	0.8	<0.5	1.1	27	0.2	0.9	0.2	82	0.11	0.022
ZSP-08 90	Soil	1.4	15.8	22.1	107	0.1	9.7	5.7	459	3.63	18.6	1.3	0.9	2.6	10	0.2	0.8	0.3	72	0.03	0.209
ZSP-08 91	Soil	1.0	16.8	14.1	59	0.3	7.8	4.9	348	6.38	16.9	0.6	<0.5	1.3	12	0.2	1.0	0.2	117	0.05	0.307
ZSP-08 92	Soil	0.8	9.9	12.1	64	0.2	6.4	4.0	347	5.52	10.9	0.5	0.5	1.1	9	0.1	1.2	0.1	103	0.05	0.129
ZSP-08 93	Soil	0.9	10.7	11.1	45	0.2	4.9	2.9	224	4.22	12.9	0.5	<0.5	1.1	9	<0.1	1.4	0.2	112	0.03	0.084
ZSP-08 94	Soil	0.5	9.4	8.1	52	0.1	8.3	4.7	270	3.22	7.5	0.5	0.7	1.3	10	0.1	0.9	0.1	67	0.03	0.046
ZSP-08 95	Soil	0.9	9.8	15.7	65	0.3	6.7	4.2	267	5.95	12.7	0.5	59.9	1.4	9	0.1	1.0	0.2	105	0.03	0.070
ZSP-08 96	Soil	0.8	12.6	13.5	117	0.2	9.6	5.9	268	4.27	12.4	0.6	<0.5	2.1	8	0.3	1.0	0.1	73	0.04	0.095
ZSP-08 97	Soil	0.6	15.0	10.1	44	0.1	8.8	4.9	225	3.18	12.0	0.5	1.1	1.6	12	<0.1	1.2	0.1	57	0.03	0.024
ZSP-08 98	Soil	0.8	15.4	12.1	106	0.1	12.5	7.5	274	4.35	15.7	0.6	<0.5	1.8	12	0.1	1.4	0.1	83	0.05	0.110
ZSP-08 99	Soil	0.6	5.8	13.9	38	0.2	3.0	1.9	125	2.79	9.5	0.4	<0.5	1.1	10	<0.1	0.7	0.2	73	0.03	0.115



AcmeLabs ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
Report Date: September 08, 2008

Page: 3 of 4 **Part** 2

CERTIFICATE OF ANALYSIS

SMI08000792.1

Method Analyte Unit MDL	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
	La ppm	Cr ppm	Mg %	Ba ppm	Ti %	B ppm	Al %	Na %	K %	W ppm	Hg ppm	Sc ppm	Tl ppm	S %	Ga ppm	Se ppm	
L158W 97 50N	Soil	10	6	0.08	59	0.004	1	1.61	0.005	0.07	0.1	0.09	1.1	0.3	<0.05	7	<0.5
L158W 98 00N	Soil	8	9	0.09	103	0.008	2	1.44	0.008	0.09	<0.1	0.04	1.1	0.4	0.11	6	1.2
L158W 98 50N	Soil	6	11	0.16	107	0.008	2	1.92	0.005	0.08	<0.1	0.09	2.0	0.3	0.05	10	0.8
L158W 99 00N	Soil	6	15	0.22	48	0.005	2	1.86	0.006	0.09	0.1	0.10	2.5	0.4	<0.05	8	1.7
L158W 100 00N	Soil	7	17	0.54	146	0.038	<1	2.75	0.022	0.06	<0.1	0.04	7.1	0.1	<0.05	6	<0.5
ZSP-08 75	Soil	4	12	0.09	29	0.011	1	1.04	0.004	0.04	0.2	0.08	2.2	<0.1	<0.05	8	<0.5
ZSP-08 76	Soil	6	6	0.03	42	0.004	2	0.85	0.007	0.04	0.1	0.02	1.5	<0.1	<0.05	4	<0.5
ZSP-08 77	Soil	4	7	0.04	31	0.003	<1	0.91	0.005	0.03	0.1	0.01	1.5	<0.1	<0.05	4	<0.5
ZSP-08 78	Soil	8	16	0.18	73	0.013	1	3.87	0.005	0.04	0.3	0.13	3.2	0.1	<0.05	12	0.5
ZSP-08 79	Soil	9	8	0.05	19	0.008	1	0.82	0.005	0.02	0.2	0.02	1.2	<0.1	<0.05	5	<0.5
ZSP-08 80	Soil	6	8	0.06	34	0.007	1	1.16	0.005	0.03	0.3	0.06	1.6	0.2	<0.05	7	0.5
ZSP-08 81	Soil	7	11	0.08	62	0.009	<1	2.59	0.005	0.04	0.3	0.16	1.7	0.1	<0.05	10	0.7
ZSP-08 82	Soil	5	8	0.03	37	0.009	2	0.81	0.007	0.03	0.2	0.04	0.9	0.1	<0.05	5	<0.5
ZSP-08 83	Soil	4	8	0.04	46	0.008	<1	1.06	0.005	0.03	0.2	0.05	1.5	0.1	<0.05	5	<0.5
ZSP-08 84	Soil	10	10	0.12	115	0.005	<1	1.63	0.006	0.04	0.1	0.08	2.0	0.1	<0.05	4	<0.5
ZSP-08 85	Soil	12	14	0.15	208	0.011	1	1.03	0.006	0.07	0.1	0.05	1.5	<0.1	<0.05	7	<0.5
ZSP-08 86	Soil	10	14	0.10	140	0.026	<1	0.98	0.008	0.06	0.1	0.04	1.6	<0.1	<0.05	7	0.6
ZSP-08 87	Soil	9	19	0.31	194	0.008	<1	2.92	0.008	0.05	0.2	0.09	3.1	0.2	<0.05	8	0.6
ZSP-08 88	Soil	16	17	0.25	244	0.009	2	3.03	0.008	0.05	0.1	0.15	2.8	0.2	<0.05	5	0.6
ZSP-08 89	Soil	8	12	0.11	292	0.029	1	0.78	0.006	0.04	0.1	0.03	2.0	0.1	<0.05	7	<0.5
ZSP-08 90	Soil	8	18	0.18	91	0.013	2	2.95	0.006	0.05	0.2	0.09	3.4	0.2	<0.05	9	<0.5
ZSP-08 91	Soil	4	27	0.26	93	0.047	2	2.89	0.008	0.03	0.2	0.20	3.9	<0.1	<0.05	11	0.6
ZSP-08 92	Soil	4	23	0.18	71	0.030	<1	2.39	0.006	0.03	0.2	0.18	2.8	<0.1	<0.05	9	0.7
ZSP-08 93	Soil	5	18	0.11	68	0.049	1	1.25	0.008	0.03	0.2	0.26	2.4	<0.1	<0.05	12	0.5
ZSP-08 94	Soil	5	23	0.23	87	0.021	1	2.18	0.007	0.04	<0.1	0.12	3.4	<0.1	<0.05	7	0.6
ZSP-08 95	Soil	5	23	0.18	71	0.038	<1	2.78	0.007	0.04	0.2	0.21	3.0	<0.1	<0.05	13	0.7
ZSP-08 96	Soil	6	22	0.22	68	0.023	1	3.78	0.006	0.06	0.2	0.12	3.2	<0.1	<0.05	7	0.5
ZSP-08 97	Soil	4	19	0.25	96	0.011	2	1.57	0.007	0.04	0.1	0.10	3.1	0.1	<0.05	4	<0.5
ZSP-08 98	Soil	4	25	0.29	99	0.021	2	3.19	0.013	0.05	0.1	0.36	4.0	<0.1	<0.05	6	0.6
ZSP-08 99	Soil	5	13	0.09	63	0.030	1	1.22	0.007	0.03	0.1	0.06	1.9	<0.1	<0.05	10	<0.5

This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
 Report Date: September 08, 2008

Page: 4 of 4 Part 1

CERTIFICATE OF ANALYSIS

SMI08000792.1

Method	Analyte	Unit	MDL	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
				Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	P
				ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	%		
ZSP-08	100	Soil		0.7	16.2	11.5	58	0.2	9.4	5.2	322	3.76	15.2	0.5	<0.5	1.4	18	0.2	1.2	0.1	67	0.08	0.152
ZSP-08	101	Soil		0.7	23.0	19.5	61	0.1	2.2	5.0	163	4.14	9.4	2.9	1.2	4.5	6	<0.1	0.4	<0.1	84	0.02	0.075
ZSP-08	102	Soil		1.1	21.2	5.9	42	0.2	3.1	4.0	132	3.63	9.3	1.8	<0.5	4.4	10	<0.1	0.8	0.3	104	0.02	0.132
ZSP-08	103	Soil		0.5	16.9	7.5	79	0.1	8.4	13.2	412	4.79	16.7	1.5	0.8	2.8	9	<0.1	0.6	0.3	143	0.02	0.064
ZSP-08	104	Soil		0.9	21.0	14.3	121	0.3	13.0	12.0	646	5.67	19.0	1.0	0.9	2.4	15	0.1	1.0	0.2	104	0.12	0.625
ZSP-08	105	Soil		0.9	8.6	11.4	76	0.1	6.5	3.8	286	4.36	11.0	0.5	1.9	1.6	9	<0.1	1.0	0.2	114	0.04	0.108
ZSP-08	106	Soil		0.8	10.8	13.5	104	<0.1	5.5	4.2	340	4.65	10.4	0.4	<0.5	1.2	9	0.1	0.8	0.2	94	0.04	0.150
ZSP-08	107	Soil		0.9	17.8	11.8	107	0.3	9.7	8.2	438	4.28	16.1	0.6	<0.5	1.7	12	0.3	1.1	0.1	78	0.05	0.078
ZSP-08	108	Soil		1.1	16.8	18.4	86	0.3	7.1	6.2	450	6.87	21.9	0.7	0.6	1.6	19	0.2	1.1	0.2	128	0.05	0.212
ZSP-08	109	Soil		0.5	13.5	7.5	98	0.1	7.3	6.6	207	3.69	8.4	0.6	8.1	1.6	10	0.2	1.0	<0.1	59	0.08	0.057
ZSP-08	110	Soil		0.8	10.8	15.6	59	0.4	5.0	3.4	229	5.59	17.1	0.5	1.0	1.5	6	0.2	1.2	0.2	142	0.03	0.079
ZSP-08	111	Soil		0.8	14.4	11.0	85	0.2	7.7	5.7	291	5.24	13.2	0.7	0.6	2.2	7	0.2	1.0	0.2	90	0.04	0.137
ZSP-08	112	Soil		1.1	11.9	13.1	50	0.1	4.8	3.2	177	5.64	15.9	0.6	1.7	2.4	8	0.1	1.2	0.1	88	0.03	0.059
ZSP-08	113	Soil		0.5	4.1	10.5	13	0.1	2.0	1.2	81	2.14	4.4	0.3	1.2	0.8	6	<0.1	0.7	0.1	56	0.02	0.014



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
 Report Date: September 08, 2008

Page: 4 of 4 Part 2

CERTIFICATE OF ANALYSIS

SMI08000792.1

Method	Analyte	Unit	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
			La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
			ppm	ppm	%	ppm	%	ppm	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
		MDL	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.05	1	0.5	
ZSP-08	100	Soil	4	18	0.24	125	0.021	2	2.20	0.006	0.04	0.1	0.14	3.2	<0.1	<0.05	5	0.6
ZSP-08	101	Soil	4	5	0.05	123	0.002	3	2.44	0.005	0.08	0.1	0.33	3.0	0.3	<0.05	3	<0.5
ZSP-08	102	Soil	12	7	0.09	38	0.012	1	1.31	0.009	0.02	0.2	0.06	4.0	<0.1	<0.05	10	<0.5
ZSP-08	103	Soil	6	31	0.05	65	0.011	2	0.83	0.002	0.03	0.1	0.05	6.5	<0.1	<0.05	5	<0.5
ZSP-08	104	Soil	7	28	0.31	122	0.044	2	4.47	0.007	0.04	0.2	0.14	6.5	<0.1	<0.05	9	0.6
ZSP-08	105	Soil	6	16	0.17	62	0.041	<1	1.50	0.006	0.04	0.2	0.07	2.8	<0.1	<0.05	12	<0.5
ZSP-08	106	Soil	4	16	0.22	72	0.038	<1	2.04	0.008	0.04	0.2	0.07	3.0	<0.1	<0.05	12	<0.5
ZSP-08	107	Soil	5	23	0.22	122	0.025	2	3.63	0.007	0.04	0.1	0.21	5.0	<0.1	<0.05	6	0.5
ZSP-08	108	Soil	5	29	0.22	155	0.052	1	3.47	0.009	0.04	0.2	0.19	4.0	<0.1	<0.05	13	0.7
ZSP-08	109	Soil	4	17	0.25	69	0.013	2	3.27	0.006	0.04	<0.1	0.12	3.8	<0.1	<0.05	4	<0.5
ZSP-08	110	Soil	4	18	0.14	74	0.021	2	3.06	0.005	0.03	0.2	0.18	3.7	0.1	<0.05	13	0.7
ZSP-08	111	Soil	4	25	0.19	58	0.012	2	3.48	0.004	0.03	0.3	0.20	5.1	0.1	<0.05	9	<0.5
ZSP-08	112	Soil	4	23	0.14	86	0.026	2	3.64	0.005	0.03	0.2	0.15	3.5	<0.1	<0.05	8	0.5
ZSP-08	113	Soil	5	10	0.05	46	0.030	<1	0.87	0.004	0.02	0.1	0.04	1.3	<0.1	<0.05	8	<0.5

QUALITY CONTROL REPORT

SMI08000792.1

Method	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
Analyte	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	P	
Unit	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	%	
MDL	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	0.001	
Pulp Duplicates																					
L158W 89 50N	Soil	5.0	56.6	64.0	58	0.5	5.9	6.4	529	8.51	88.2	0.7	194.0	1.2	7	0.3	2.2	0.7	82	0.04	0.091
REP L158W 89 50N	QC	4.7	53.7	61.6	55	0.4	6.0	6.2	494	8.34	83.0	0.7	228.3	1.2	7	0.3	2.1	0.7	80	0.04	0.079
L158W 92 00N	Soil	2.2	51.3	52.1	95	0.2	11.7	6.8	403	5.96	65.3	0.7	8.4	0.7	14	0.9	2.2	0.9	68	0.11	0.060
REP L158W 92 00N	QC	2.3	49.2	51.1	97	0.2	11.4	6.7	387	5.90	63.2	0.7	10.4	0.7	14	0.8	2.5	0.9	68	0.10	0.058
ZSP-08 89	Soil	1.3	13.9	14.2	69	0.1	6.2	3.6	230	2.93	15.8	0.8	<0.5	1.1	27	0.2	0.9	0.2	82	0.11	0.022
REP ZSP-08 89	QC	1.2	14.2	14.0	68	0.1	6.6	3.8	227	2.91	15.8	0.8	0.9	1.1	28	0.2	1.0	0.2	79	0.12	0.023
ZSP-08 98	Soil	0.8	15.4	12.1	106	0.1	12.5	7.5	274	4.35	15.7	0.6	<0.5	1.8	12	0.1	1.4	0.1	83	0.05	0.110
REP ZSP-08 98	QC	0.8	14.5	11.5	107	0.1	12.5	7.5	267	4.28	15.8	0.6	3.2	1.8	12	0.2	1.3	0.1	81	0.05	0.113
Reference Materials																					
STD DS7	Standard	20.3	121.6	70.2	409	0.9	58.5	10.1	667	2.50	53.1	5.1	62.6	4.6	74	6.2	6.2	4.6	88	0.95	0.078
STD DS7	Standard	17.9	105.0	66.4	376	0.8	51.0	9.4	626	2.36	48.3	4.8	60.0	4.2	65	5.4	5.5	4.3	83	0.87	0.069
STD DS7	Standard	18.1	97.9	66.4	359	0.7	46.4	8.8	611	2.21	45.2	4.7	83.7	4.7	73	5.3	5.7	4.1	82	0.91	0.066
STD DS7 Expected		20.9	109	70.6	411	0.9	56	9.7	627	2.39	48.2	4.9	70	4.4	69	6.4	5.9	4.5	86	0.93	0.08
BLK	Blank	<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01	<0.001
BLK	Blank	<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01	<0.001
BLK	Blank	<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01	<0.001

QUALITY CONTROL REPORT

SMI08000792.1

Method	Analyte	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
		La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
Unit		ppm	ppm	%	ppm	%	ppm	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
MDL		1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.05	1	0.5	
Pulp Duplicates																	
L158W 89 50N	Soil	6	15	0.19	70	0.011	2	1.88	0.005	0.05	0.2	0.10	2.7	0.3	<0.05	11	1.4
REP L158W 89 50N	QC	6	15	0.17	67	0.011	1	1.81	0.005	0.05	0.1	0.10	2.5	0.3	<0.05	10	1.1
L158W 92 00N	Soil	7	18	0.25	77	0.010	2	2.08	0.008	0.08	<0.1	0.09	2.7	0.3	<0.05	8	0.6
REP L158W 92 00N	QC	7	17	0.25	73	0.011	3	2.08	0.007	0.08	0.1	0.11	2.9	0.2	0.09	8	1.1
ZSP-08 89	Soil	8	12	0.11	292	0.029	1	0.78	0.006	0.04	0.1	0.03	2.0	0.1	<0.05	7	<0.5
REP ZSP-08 89	QC	8	12	0.11	302	0.030	<1	0.80	0.007	0.04	0.2	0.04	2.0	0.1	<0.05	7	<0.5
ZSP-08 98	Soil	4	25	0.29	99	0.021	2	3.19	0.013	0.05	0.1	0.36	4.0	<0.1	<0.05	6	0.6
REP ZSP-08 98	QC	4	25	0.28	97	0.022	2	3.09	0.007	0.05	0.1	0.19	3.9	<0.1	<0.05	6	0.7
Reference Materials																	
STD DS7	Standard	13	173	1.08	411	0.129	37	1.03	0.090	0.49	4.0	0.21	2.7	4.2	0.20	5	3.6
STD DS7	Standard	12	163	1.03	346	0.118	38	0.96	0.079	0.44	3.8	0.20	2.4	4.2	0.17	5	3.5
STD DS7	Standard	14	164	0.99	350	0.133	36	1.03	0.084	0.45	4.1	0.16	2.8	4.3	0.19	5	3.7
STD DS7 Expected		13	163	1.05	370	0.124	39	0.959	0.073	0.44	3.8	0.2	2.5	4.2	0.21	5	3.5
BLK	Blank	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
BLK	Blank	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
BLK	Blank	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.

Vancouver BC V6C 1Z7 Canada

Submitted By:

Glen Garratt

Receiving Lab:

Canada-Smithers

Received:

August 25, 2008

Report Date:

September 08, 2008

Page:

1 of 2

CERTIFICATE OF ANALYSIS

SMI08000802.1

CLIENT JOB INFORMATION

Project: Zymo
Shipment ID: zy-rk-08-14
P.O. Number
Number of Samples: 16

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
DISP-RJT Dispose of Reject After 90 days

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Mincord Exploration Consultants Ltd.
110 - 325 Howe St.
Vancouver BC V6C 1Z7
Canada

CC: Bob Johnston

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status
R150	16	Crush, split and pulverize rock to 200 mesh		
1DX15	16	1:1:1 Aqua Regia digestion ICP-MS analysis	15	Completed

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only. All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**

110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo

Report Date: September 08, 2008

Page: 2 of 2 Part 1

CERTIFICATE OF ANALYSIS

SMI08000802.1

Method	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
Unit	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	ppm	
MDL	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	
726747	Rock	1.80	7.8	6688	104.3	123	6.6	9.7	59.7	674	27.70	4240	1.7	799.1	1.1	32	0.9	134.9	5.3	15	2.84
726748	Rock	1.94	1.7	25.2	5.1	63	<0.1	9.2	11.1	923	3.31	14.3	0.1	<0.5	0.6	80	0.1	0.8	0.1	36	2.35
726749	Rock	1.97	0.6	72.7	4.6	69	<0.1	16.1	16.4	1726	3.96	50.5	0.2	2.4	0.7	268	0.1	3.2	<0.1	76	5.59
726750	Rock	1.80	1.1	31.0	5.9	73	<0.1	8.6	12.0	814	3.63	18.8	0.2	1.2	1.0	48	<0.1	0.5	0.1	37	1.12
726751	Rock	2.22	3.9	50.8	8.2	96	<0.1	8.6	19.5	1194	4.13	6.0	1.6	1.4	4.3	93	0.3	0.4	<0.1	124	3.46
726752	Rock	2.56	2.0	49.7	4.7	84	<0.1	9.2	21.6	1521	4.97	0.6	0.6	<0.5	2.4	51	<0.1	<0.1	<0.1	93	1.64
726753	Rock	2.25	3.4	39.7	16.5	75	0.4	62.3	16.1	501	3.42	36.6	1.0	1.2	3.4	9	0.2	0.8	0.1	37	0.14
726754	Rock	1.95	2.8	30.0	7.4	84	<0.1	6.7	13.5	784	4.42	19.8	0.9	1.2	2.6	50	0.2	0.2	0.3	67	0.72
726755	Rock	2.09	2.1	26.3	8.2	56	<0.1	5.1	12.8	1034	3.55	9.0	1.9	<0.5	4.8	65	0.1	0.2	0.1	77	1.45
726756	Rock	2.22	2.2	19.9	103.3	227	0.2	17.8	6.8	648	3.28	33.3	0.4	14.6	2.2	3	0.2	1.1	0.1	17	0.02
726757	Rock	2.32	11.8	89.4	8.9	69	0.2	86.0	17.8	663	4.83	109.0	0.6	8.8	3.7	9	0.1	2.5	0.4	43	0.08
726758	Rock	1.97	26.1	23.6	8.2	85	0.1	35.3	11.3	298	2.58	11.6	0.5	12.3	3.6	12	0.7	0.5	1.3	14	0.30
726759	Rock	2.30	6.5	1007	193.8	320	5.0	44.4	9.3	2861	3.57	132.3	0.8	217.0	2.9	20	1.5	20.0	2.1	12	1.62
726760	Rock	2.05	2.6	80.2	37.5	234	0.2	16.5	16.5	786	4.48	304.0	0.8	46.8	4.4	63	0.8	2.9	1.2	121	0.71
726761	Rock	1.97	56.9	69.6	13.4	27	0.2	6.3	3.1	167	1.77	27.2	0.2	9.2	0.9	11	<0.1	0.9	0.5	9	0.16
726762	Rock	2.30	1.0	192.0	23.7	102	0.3	10.7	11.1	586	5.10	34.0	1.0	12.9	4.8	70	0.3	0.8	2.1	105	1.51



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
 Report Date: September 08, 2008

Page: 2 of 2 Part 2

CERTIFICATE OF ANALYSIS

SMI08000802.1

Method	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se	
Unit	%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
MDL	0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.01	0.01	0.1	0.01	0.05	1	0.5	
726747	Rock	0.019	<1	3	0.31	2	<0.001	<1	0.05	0.002	0.05	2.1	3.84	1.6	94.0	>10	<1	14.9
726748	Rock	0.061	8	10	0.57	156	<0.001	2	0.87	0.024	0.13	1.6	0.10	6.4	<0.1	0.06	3	<0.5
726749	Rock	0.057	6	15	1.40	179	<0.001	<1	0.37	0.005	0.05	0.4	0.10	11.5	0.3	0.09	1	<0.5
726750	Rock	0.055	7	7	0.62	126	<0.001	2	0.73	0.028	0.14	0.9	0.10	6.4	<0.1	<0.05	2	<0.5
726751	Rock	0.155	23	6	1.20	785	0.005	1	1.95	0.026	0.05	0.3	0.10	8.2	<0.1	0.09	9	<0.5
726752	Rock	0.180	25	7	1.79	713	0.002	2	2.60	0.023	0.13	0.6	0.06	5.1	<0.1	<0.05	11	<0.5
726753	Rock	0.045	11	25	0.23	154	<0.001	<1	0.83	0.013	0.14	0.3	0.01	3.6	0.2	0.47	3	<0.5
726754	Rock	0.170	14	5	0.90	384	0.002	1	1.47	0.021	0.15	0.3	0.01	5.1	0.1	0.30	6	<0.5
726755	Rock	0.137	32	6	0.97	150	0.003	<1	1.27	0.039	0.07	0.3	0.01	4.6	<0.1	0.21	8	<0.5
726756	Rock	0.037	12	14	0.02	80	<0.001	<1	0.24	0.004	0.12	0.3	0.30	1.9	0.1	<0.05	<1	<0.5
726757	Rock	0.067	10	53	0.93	93	0.003	2	2.15	0.015	0.24	0.6	0.08	3.6	0.2	0.61	5	0.7
726758	Rock	0.048	10	12	0.11	96	<0.001	<1	0.40	0.021	0.24	0.2	0.18	2.3	0.4	1.23	<1	1.0
726759	Rock	0.061	7	14	0.35	169	0.001	1	0.34	0.008	0.19	0.3	0.26	2.4	0.4	0.76	<1	2.0
726760	Rock	0.172	16	6	1.47	180	0.002	2	2.98	0.127	0.13	0.2	0.67	9.1	0.5	0.42	9	1.1
726761	Rock	0.092	3	5	0.02	292	<0.001	2	0.60	0.019	0.18	0.3	0.03	1.9	0.2	0.27	1	<0.5
726762	Rock	0.163	15	10	1.81	66	0.008	2	2.40	0.076	0.12	0.3	0.03	7.8	0.2	2.14	9	0.8

QUALITY CONTROL REPORT

SMI08000802.1

Method	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
Unit	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	
MDL	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	
Pulp Duplicates																					
726750	Rock	1.80	1.1	31.0	5.9	73	<0.1	8.6	12.0	814	3.63	18.8	0.2	1.2	1.0	48	<0.1	0.5	0.1	37	1.12
REP 726750	QC		1.2	31.6	6.0	70	<0.1	9.6	11.6	822	3.66	18.7	0.1	1.6	1.2	48	0.1	0.5	0.1	38	1.13
Reference Materials																					
STD DS7	Standard		19.2	112.3	74.2	405	0.9	56.7	10.1	677	2.51	51.1	5.1	64.0	4.4	69	5.5	6.1	4.6	89	0.92
STD DS7	Standard		19.4	108.2	69.0	384	0.8	53.6	9.7	661	2.44	48.0	5.0	62.5	4.2	67	5.4	5.7	4.2	86	0.91
STD DS7 Expected			20.9	109	70.6	411	0.9	56	9.7	627	2.39	48.2	4.9	70	4.4	69	6.4	5.9	4.5	86	0.93
BLK	Blank		<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01
Prep Wash																					
G1	Prep Blank	<0.01	1.6	3.4	2.4	45	<0.1	4.9	4.5	560	1.92	<0.5	1.9	<0.5	3.4	56	<0.1	<0.1	0.1	41	0.51
G1	Prep Blank	<0.01	1.1	3.8	2.6	49	<0.1	5.8	5.0	595	2.09	<0.5	1.9	0.6	4.1	57	<0.1	<0.1	<0.1	44	0.54

QUALITY CONTROL REPORT

SMI08000802.1

Method		1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte		P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
Unit		%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm
MDL		0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5
Pulp Duplicates																		
726750	Rock	0.055	7	7	0.62	126	<0.001	2	0.73	0.028	0.14	0.9	0.10	6.4	<0.1	<0.05	2	<0.5
REP 726750	QC	0.053	7	7	0.62	127	<0.001	3	0.72	0.027	0.14	0.8	0.10	6.4	<0.1	<0.05	2	<0.5
Reference Materials																		
STD DS7	Standard	0.076	12	165	1.13	396	0.127	39	1.05	0.079	0.50	4.2	0.21	2.4	4.4	0.19	5	3.5
STD DS7	Standard	0.072	12	161	1.08	390	0.130	37	1.03	0.077	0.48	3.8	0.20	2.5	4.1	0.19	5	3.5
STD DS7 Expected		0.08	13	163	1.05	370	0.124	39	0.959	0.073	0.44	3.8	0.2	2.5	4.2	0.21	4.6	3.5
BLK	Blank	<0.001	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
Prep Wash																		
G1	Prep Blank	0.078	6	12	0.58	219	0.130	<1	0.91	0.059	0.47	9.4	<0.01	1.8	0.4	<0.05	5	<0.5
G1	Prep Blank	0.084	7	14	0.64	237	0.140	<1	1.01	0.073	0.52	4.9	<0.01	2.3	0.4	<0.05	5	<0.5



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.

Vancouver BC V6C 1Z7 Canada

Submitted By:

Glen Garratt

Receiving Lab:

Canada-Smithers

Received:

August 26, 2008

Report Date:

September 09, 2008

Page:

1 of 3

CERTIFICATE OF ANALYSIS

SMI08000818.1

CLIENT JOB INFORMATION

Project: Zymo
Shipment ID: zy-so-08-14
P.O. Number
Number of Samples: 35

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
DISP-RJT-SOIL Immediate Disposal of Soil Reject

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Mincord Exploration Consultants Ltd.
110 - 325 Howe St.
Vancouver BC V6C 1Z7
Canada

CC: Bob Johnston

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status
SS80	35	Dry at 60C sieve 100g to -80 mesh		
Dry at 60C	35	Dry at 60C		
1DX15	35	1:1:1 Aqua Regia digestion ICP-MS analysis	15	Completed

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only. All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.

110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo

Report Date: September 09, 2008

Page: 2 of 3 Part 1

CERTIFICATE OF ANALYSIS

SMI08000818.1

Method	Analyte	Unit	MDL	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15		
				Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	P
				ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	
				0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	2	0.01	0.001	
L162W 82 00N	Soil			3.0	17.5	27.1	41	0.2	3.7	9.9	3098	4.43	32.3	0.7	8.3	0.8	15	<0.1	0.8	0.6	70	0.08	0.060
L162W 82 50N	Soil			3.5	54.6	42.4	89	0.5	8.5	5.5	263	4.77	41.7	0.7	8.4	1.3	9	0.3	1.5	0.6	94	0.02	0.045
L162W 83 00N	Soil			5.7	86.9	50.2	113	0.5	8.1	5.1	366	7.90	62.6	0.7	9.6	2.0	6	0.3	1.5	1.0	94	0.02	0.060
L162W 84 50N	Soil			6.7	157.1	71.7	201	1.3	13.5	18.3	1332	6.51	85.4	2.7	23.4	1.1	12	0.6	1.9	1.0	74	0.08	0.125
L162W 85 00N	Soil			10.1	75.4	39.2	70	0.4	10.1	12.5	859	8.61	37.8	1.0	23.2	1.0	7	0.2	1.3	0.8	113	0.06	0.090
L162W 85 50N	Soil			6.4	39.3	38.7	54	0.9	10.0	3.5	233	5.62	44.3	0.8	11.2	0.3	9	0.2	1.2	0.9	94	0.06	0.121
L162W 86 00N	Soil			5.9	64.9	51.8	57	0.5	5.7	4.7	204	6.82	74.5	0.7	13.9	1.7	6	0.2	1.5	1.2	87	0.02	0.106
L162W 86 50N	Soil			3.5	78.5	100.8	117	0.3	9.5	8.6	452	7.90	74.5	0.9	13.1	2.8	5	0.2	1.7	0.8	70	0.04	0.130
L162W 87 00N	Soil			3.5	73.6	39.1	121	<0.1	17.7	16.7	6492	4.98	47.0	1.0	6.6	1.3	12	0.2	1.7	0.6	69	0.05	0.077
L162W 87 50N	Soil			2.2	49.1	27.8	76	0.2	12.4	5.2	207	3.69	34.0	1.0	9.4	0.5	12	0.1	1.7	0.5	71	0.04	0.079
L162W 88 00N	Soil			3.1	30.3	27.1	66	0.1	6.5	10.8	1271	5.29	32.0	0.5	4.4	1.0	13	0.2	0.9	0.4	85	0.09	0.051
L162W 88 50N	Soil			2.7	48.1	38.1	69	0.3	8.0	5.8	305	8.71	40.5	0.9	7.6	1.1	8	0.1	1.1	0.8	91	0.03	0.094
L162W 89 00N	Soil			2.4	35.6	26.0	56	0.3	7.0	3.7	207	7.27	31.5	0.5	1.9	1.2	8	<0.1	1.3	0.4	122	0.02	0.069
L162W 89 50N	Soil			3.6	51.3	51.7	53	0.7	6.7	5.9	318	12.61	47.5	0.6	5.8	1.8	5	0.1	1.1	0.6	129	0.02	0.131
L162W 90 00N	Soil			3.1	76.9	42.8	106	0.3	8.0	7.2	608	6.03	41.2	0.8	9.6	1.3	6	0.4	1.3	0.6	86	0.04	0.126
L162W 90 50N	Soil			2.1	37.4	28.7	61	0.3	7.1	5.2	429	9.22	26.1	0.4	2.7	1.0	6	<0.1	0.7	0.4	98	0.02	0.118
L162W 91 00N	Soil			6.8	115.4	89.6	185	1.9	9.8	14.7	746	8.15	90.1	1.4	25.5	2.6	12	0.6	1.6	1.6	74	0.08	0.142
L162W 91 50N	Soil			3.9	135.0	53.5	192	0.3	21.2	21.2	999	4.85	44.0	0.8	13.5	1.7	8	0.4	1.7	0.6	60	0.06	0.076
L162W 92 00N	Soil			6.3	49.1	34.5	51	0.5	4.7	3.8	252	8.67	28.7	0.8	6.3	1.4	4	0.2	1.3	0.7	138	0.02	0.084
L162W 92 50N	Soil			4.1	63.0	24.3	72	0.5	8.0	4.6	245	5.44	27.8	0.5	6.9	0.8	3	0.2	1.3	0.8	65	0.02	0.064
L162W 93 00N	Soil			3.0	49.8	23.6	79	0.3	9.0	8.1	633	4.80	30.0	0.5	13.2	0.8	5	0.3	1.1	0.4	60	0.02	0.071
L162W 93 50N	Soil			3.2	61.0	40.0	89	0.3	9.9	5.6	274	6.07	35.4	0.5	9.4	1.1	3	0.2	1.5	0.6	63	0.01	0.074
L162W 94 00N	Soil			3.4	48.9	23.5	61	0.4	7.1	4.7	245	4.74	32.1	0.8	3.7	0.3	4	0.3	1.3	0.5	88	0.02	0.074
L162W 94 50N	Soil			3.1	69.8	23.8	82	0.3	11.0	5.6	261	5.06	29.8	1.2	8.0	0.6	7	0.2	1.4	0.5	69	0.03	0.087
L162W 95 00N	Soil			2.6	48.4	19.1	88	0.2	18.8	7.6	407	7.36	24.9	0.5	5.4	1.4	3	0.1	1.5	0.2	76	0.01	0.101
L162W 95 50N	Soil			1.1	35.1	10.5	72	<0.1	28.3	9.0	361	3.84	16.4	0.4	<0.5	0.6	5	0.1	0.8	0.2	68	0.02	0.068
L162W 96 00N	Soil			2.2	48.3	20.1	64	<0.1	14.2	6.6	558	5.04	25.0	0.4	5.4	0.8	4	0.2	1.4	0.3	80	0.01	0.136
L162W 96 50N	Soil			2.4	63.5	19.5	84	0.4	19.3	7.0	342	5.95	27.7	0.6	3.9	1.2	5	0.4	1.8	0.4	65	0.02	0.070
L162W 97 00N	Soil			3.4	69.6	27.3	78	0.7	14.7	6.6	325	6.09	29.4	0.4	4.5	1.1	5	0.2	1.6	0.5	70	0.02	0.085
L162W 97 50N	Soil			1.4	48.0	15.4	93	0.1	38.8	13.8	435	4.15	19.9	0.5	3.5	1.1	11	0.3	1.6	0.2	59	0.06	0.055

This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.



AcmeLabs ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
Report Date: September 09, 2008

Page: 2 of 3 **Part** 2

CERTIFICATE OF ANALYSIS

SMI08000818.1

Method	Analyte	Unit	MDL	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15		
				La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
				ppm	ppm	%	ppm	%	ppm	%	ppm	ppm	ppm	ppm	%	ppm	ppm		
				1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.01	0.05	0.5		
L162W 82 00N	Soil			9	6	0.14	161	0.014	2	1.37	0.005	0.07	0.1	0.06	1.9	0.3	<0.05	8	<0.5
L162W 82 50N	Soil			6	15	0.18	65	0.016	3	1.64	0.006	0.06	0.1	0.10	3.0	0.3	<0.05	9	0.8
L162W 83 00N	Soil			6	17	0.22	49	0.009	4	2.26	0.008	0.06	0.1	0.17	3.8	0.3	<0.05	10	1.1
L162W 84 50N	Soil			20	16	0.31	88	0.010	3	2.28	0.008	0.07	<0.1	0.22	6.2	0.2	<0.05	7	2.9
L162W 85 00N	Soil			11	22	0.38	58	0.015	3	2.11	0.006	0.05	<0.1	0.16	4.0	0.2	0.07	13	2.1
L162W 85 50N	Soil			7	11	0.07	54	0.014	2	1.18	0.005	0.05	0.1	0.13	1.4	0.2	<0.05	12	1.4
L162W 86 00N	Soil			6	13	0.15	51	0.008	4	2.00	0.006	0.04	0.1	0.14	2.8	0.2	<0.05	9	1.2
L162W 86 50N	Soil			7	23	0.22	52	0.009	2	5.64	0.006	0.05	<0.1	0.34	5.0	0.2	<0.05	7	1.8
L162W 87 00N	Soil			8	22	0.34	98	0.006	4	2.47	0.009	0.12	<0.1	0.12	4.1	0.2	<0.05	7	1.0
L162W 87 50N	Soil			6	19	0.27	133	0.007	3	1.97	0.006	0.09	0.1	0.13	2.1	0.2	<0.05	8	1.1
L162W 88 00N	Soil			7	13	0.27	160	0.003	2	2.10	0.010	0.06	<0.1	0.06	3.4	0.1	<0.05	9	0.7
L162W 88 50N	Soil			6	24	0.29	52	0.011	1	2.62	0.007	0.05	<0.1	0.21	3.9	0.2	<0.05	10	1.6
L162W 89 00N	Soil			5	21	0.17	48	0.010	2	2.46	0.006	0.06	<0.1	0.15	3.5	0.1	<0.05	15	<0.5
L162W 89 50N	Soil			4	24	0.17	44	0.011	1	2.67	0.005	0.04	0.1	0.17	3.5	0.1	<0.05	17	1.3
L162W 90 00N	Soil			7	14	0.24	58	0.008	2	2.80	0.007	0.04	0.1	0.16	3.5	0.2	<0.05	8	1.4
L162W 90 50N	Soil			4	20	0.22	50	0.005	<1	2.45	0.009	0.05	<0.1	0.10	3.3	0.1	<0.05	11	<0.5
L162W 91 00N	Soil			11	18	0.25	73	0.005	1	3.11	0.006	0.05	<0.1	0.29	5.4	0.2	<0.05	8	2.3
L162W 91 50N	Soil			8	16	0.41	70	0.005	<1	2.70	0.008	0.06	<0.1	0.13	5.8	0.2	0.06	5	1.4
L162W 92 00N	Soil			5	16	0.15	53	0.019	2	2.50	0.005	0.03	0.4	0.16	2.8	0.1	0.06	17	1.1
L162W 92 50N	Soil			5	13	0.21	40	0.005	<1	1.91	0.006	0.03	0.1	0.13	2.7	0.1	<0.05	7	0.7
L162W 93 00N	Soil			7	12	0.20	65	0.004	1	2.01	0.008	0.04	<0.1	0.11	3.1	0.1	0.07	6	0.6
L162W 93 50N	Soil			4	11	0.18	39	0.005	1	1.72	0.004	0.03	0.1	0.09	2.6	0.2	0.06	6	0.7
L162W 94 00N	Soil			5	11	0.18	51	0.007	<1	1.72	0.006	0.04	<0.1	0.11	2.0	0.1	0.06	10	0.6
L162W 94 50N	Soil			7	14	0.28	63	0.009	1	2.12	0.007	0.04	<0.1	0.10	3.0	<0.1	0.07	8	1.3
L162W 95 00N	Soil			3	25	0.29	46	0.005	<1	2.85	0.006	0.04	<0.1	0.17	3.8	0.2	<0.05	7	1.4
L162W 95 50N	Soil			3	24	0.17	49	0.006	2	1.44	0.004	0.07	0.1	0.12	3.6	0.1	<0.05	6	<0.5
L162W 96 00N	Soil			4	18	0.16	54	0.006	1	1.57	0.005	0.05	<0.1	0.13	3.2	0.1	<0.05	7	0.7
L162W 96 50N	Soil			4	23	0.27	57	0.004	2	2.41	0.010	0.05	<0.1	0.26	3.5	0.2	<0.05	7	1.2
L162W 97 00N	Soil			4	18	0.24	54	0.005	1	2.07	0.005	0.04	0.1	0.14	3.5	0.2	<0.05	6	0.8
L162W 97 50N	Soil			4	19	0.22	160	0.004	2	1.59	0.006	0.06	<0.1	0.44	5.1	0.1	<0.05	4	1.0

This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.

Vancouver BC V6C 1Z7 Canada

Project:

Zymo

Report Date:

September 09, 2008

Page:

3 of 3

Part 1

CERTIFICATE OF ANALYSIS

SMI08000818.1

Method	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	P	
Unit	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	%	
MDL	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	0.001	
L162W 98 00N Soil	1.9	52.7	17.1	71	0.1	17.7	6.5	265	3.69	18.8	0.4	5.2	0.7	33	0.2	1.1	0.4	55	0.28	0.069	
L162W 98 50N Soil	1.7	81.3	15.8	93	0.1	36.2	12.4	420	4.07	21.9	0.5	3.7	1.3	8	0.5	1.5	0.3	61	0.03	0.051	
L162W 99 00N Soil	1.2	27.6	10.3	60	<0.1	15.3	6.9	381	4.90	17.9	0.6	2.0	0.2	18	0.2	0.9	0.2	76	0.11	0.086	
L162W 99 50N Soil	1.9	64.3	24.4	96	0.2	21.0	11.0	411	4.66	20.5	1.1	5.3	1.8	13	0.2	1.1	0.2	72	0.05	0.068	
L162W 100 00N Soil	1.1	30.8	9.0	69	0.2	13.8	7.0	652	5.08	15.8	0.4	2.0	0.2	7	0.4	0.7	0.2	71	0.07	0.098	



AcmeLabs ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
Report Date: September 09, 2008

Page: 3 of 3 **Part** 2

CERTIFICATE OF ANALYSIS

SMI08000818.1

Method	Analyte	Unit	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15		
			La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se	
			ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm
			MDL	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5
L162W	98 00N	Soil	5	15	0.33	319	0.004	<1	1.62	0.008	0.05	<0.1	0.07	3.5	0.1	<0.05	5	<0.5	
L162W	98 50N	Soil	5	22	0.28	115	0.004	2	1.73	0.005	0.07	<0.1	0.23	5.6	0.1	<0.05	5	0.6	
L162W	99 00N	Soil	3	17	0.39	67	0.009	<1	1.91	0.006	0.05	<0.1	0.11	2.1	<0.1	<0.05	7	<0.5	
L162W	99 50N	Soil	9	22	0.38	80	0.009	3	3.60	0.006	0.05	0.2	0.25	5.3	0.1	<0.05	6	1.0	
L162W	100 00N	Soil	4	16	0.37	87	0.009	2	2.26	0.005	0.04	<0.1	0.13	2.0	<0.1	<0.05	8	<0.5	

QUALITY CONTROL REPORT

SMI08000818.1

Method	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
Analyte	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	P	
Unit	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	%	
MDL	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	0.001	
Pulp Duplicates																					
L162W 90 50N	Soil	2.1	37.4	28.7	61	0.3	7.1	5.2	429	9.22	26.1	0.4	2.7	1.0	6	<0.1	0.7	0.4	98	0.02	0.118
REP L162W 90 50N	QC	2.0	37.6	29.4	62	0.4	7.0	5.3	420	9.23	25.8	0.4	4.1	1.0	5	0.1	0.6	0.4	91	0.01	0.121
L162W 95 50N	Soil	1.1	35.1	10.5	72	<0.1	28.3	9.0	361	3.84	16.4	0.4	<0.5	0.6	5	0.1	0.8	0.2	68	0.02	0.068
REP L162W 95 50N	QC	1.2	36.0	10.7	72	<0.1	27.4	9.5	349	3.83	16.4	0.5	1.1	0.6	8	0.2	0.7	0.2	71	0.02	0.067
Reference Materials																					
STD DS7	Standard	17.7	104.6	63.6	397	0.8	51.5	8.5	572	2.23	51.9	4.4	70.7	3.5	63	5.6	5.6	4.2	83	0.82	0.073
STD DS7	Standard	19.8	100.5	68.4	393	0.8	50.1	9.0	638	2.41	53.5	4.9	104.1	4.8	84	6.2	6.1	4.6	94	1.01	0.081
STD DS7 Expected		20.9	109	70.6	411	0.9	56	9.7	627	2.39	48.2	4.9	70	4.4	69	6.4	5.9	4.5	86	0.93	0.08
BLK	Blank	<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01	<0.001
BLK	Blank	<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01	<0.001

QUALITY CONTROL REPORT

SMI08000818.1

Method	Analyte	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
		La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
Unit		ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm
MDL		1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5
Pulp Duplicates																	
L162W 90 50N	Soil	4	20	0.22	50	0.005	<1	2.45	0.009	0.05	<0.1	0.10	3.3	0.1	<0.05	11	<0.5
REP L162W 90 50N	QC	4	19	0.22	50	0.003	<1	2.40	0.008	0.04	<0.1	0.14	3.2	0.1	<0.05	11	0.9
L162W 95 50N	Soil	3	24	0.17	49	0.006	2	1.44	0.004	0.07	0.1	0.12	3.6	0.1	<0.05	6	<0.5
REP L162W 95 50N	QC	3	24	0.18	51	0.009	2	1.51	0.007	0.07	<0.1	0.12	3.3	0.1	<0.05	6	0.6
Reference Materials																	
STD DS7	Standard	10	155	0.99	331	0.101	36	0.92	0.094	0.43	3.9	0.20	2.9	4.3	0.21	4	3.7
STD DS7	Standard	15	164	1.05	392	0.129	43	1.11	0.116	0.49	3.6	0.20	3.3	4.2	0.21	5	3.8
STD DS7 Expected		13	163	1.05	370	0.124	39	0.959	0.073	0.44	3.8	0.2	2.5	4.2	0.21	5	3.5
BLK	Blank	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
BLK	Blank	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.

Vancouver BC V6C 1Z7 Canada

Submitted By:

Glen Garratt

Receiving Lab:

Canada-Smithers

Received:

September 09, 2008

Report Date:

October 03, 2008

Page:

1 of 3

CERTIFICATE OF ANALYSIS

SMI08000894.1

CLIENT JOB INFORMATION

Project: Zymo
Shipment ID: zy-so-08-16
P.O. Number
Number of Samples: 44

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
DISP-RJT-SOIL Immediate Disposal of Soil Reject

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Mincord Exploration Consultants Ltd.
110 - 325 Howe St.
Vancouver BC V6C 1Z7
Canada

CC: Bob Johnston

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status
SS80	44	Dry at 60C sieve 100g to -80 mesh		
Dry at 60C	44	Dry at 60C		
1DX15	44	1:1:1 Aqua Regia digestion ICP-MS analysis	15	Completed

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only. All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.

Vancouver BC V6C 1Z7 Canada

Project:

Zymo

Report Date:

October 03, 2008

Page:

2 of 3

Part 1

CERTIFICATE OF ANALYSIS

SMI08000894.1

Method Analyte Unit MDL	1DX15																				
	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	P	
	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	%	
	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	0.001	
L98W 93 50N	Soil	2.2	80.0	110.8	153	8.4	11.3	8.0	748	3.89	103.3	2.5	91.8	0.3	8	0.7	2.9	4.8	57	0.02	0.085
L98W 94 00N	Soil	2.8	88.2	345.7	368	3.0	13.1	13.2	1753	5.27	238.3	1.4	51.3	1.4	7	0.7	2.9	6.0	49	0.03	0.148
L98W 94 50N	Soil	1.6	31.7	146.5	155	1.1	9.5	4.8	371	3.85	88.7	0.7	18.4	0.2	8	0.3	1.7	5.9	79	0.02	0.058
L98W 95 00N	Soil	1.7	136.2	144.5	259	3.5	18.1	9.1	755	4.53	63.8	2.5	16.1	0.8	12	1.3	2.1	1.8	76	0.04	0.075
L98W 95 50N	Soil	1.8	60.2	67.5	137	1.0	14.2	7.6	499	4.73	41.5	1.5	5.7	0.8	10	0.4	2.3	0.8	83	0.03	0.070
L98W 96 00N	Soil	2.7	42.0	96.2	148	0.4	11.7	6.1	428	5.33	74.0	1.1	18.5	1.6	11	0.3	2.3	1.7	77	0.02	0.118
L98W 96 50N	Soil	1.1	21.9	38.9	73	0.2	7.7	4.3	568	3.55	28.9	0.5	2.7	0.5	9	0.1	1.7	0.9	77	0.02	0.074
L98W 97 00N	Soil	1.2	29.4	36.7	189	0.2	9.9	4.7	329	3.84	24.3	1.5	2.3	0.1	12	0.6	1.1	0.6	74	0.07	0.078
L98W 97 50N	Soil	1.7	18.6	32.6	65	0.2	8.9	4.9	464	5.62	26.4	0.8	1.0	0.2	11	0.2	1.6	0.5	103	0.02	0.148
L98W 98 50N	Soil	1.2	26.0	30.4	53	1.6	7.7	4.0	268	3.72	36.0	0.5	3.1	0.3	9	0.4	1.6	0.5	86	<0.01	0.054
L98W 99 00N	Soil	1.6	38.8	112.6	176	0.6	7.8	4.5	936	4.88	55.2	0.6	7.0	0.7	5	0.1	2.1	2.1	76	<0.01	0.075
L98W 99 50N	Soil	2.2	61.3	130.0	220	0.2	11.2	7.8	920	4.84	74.1	0.6	15.4	1.0	6	0.3	3.2	2.6	59	0.01	0.072
L98W 100 00N	Soil	0.8	20.8	226.4	318	2.3	1.7	2.3	446	2.38	36.5	1.4	4.0	3.9	3	0.3	0.3	3.2	27	<0.01	0.067
L98W 100 50N	Soil	11.4	66.6	175.7	167	0.7	4.9	4.4	717	5.54	36.2	1.3	5.3	1.6	7	0.5	1.1	2.1	37	0.02	0.191
L98W 101 00N	Soil	2.1	39.6	88.8	275	0.9	20.0	11.4	934	4.59	35.0	4.6	19.7	0.3	26	0.4	1.4	2.0	63	0.25	0.118
L98W 101 50N	Soil	2.0	29.3	89.8	149	0.8	5.8	3.9	473	6.15	48.7	1.1	13.6	0.6	5	0.7	1.4	2.2	61	0.04	0.083
L98W 102 00N	Soil	1.7	35.0	123.9	194	0.5	14.7	8.4	495	4.79	48.7	1.1	6.9	0.8	12	0.8	1.8	0.6	65	0.06	0.084
L98W 102 50N	Soil	2.4	19.7	38.8	67	0.6	6.2	3.9	245	4.46	44.3	1.2	5.5	1.6	7	0.2	1.2	2.7	92	0.02	0.085
L98W 103 00N	Soil	1.5	24.5	13.4	33	0.2	10.6	3.6	132	1.86	22.5	0.3	1.6	0.2	7	<0.1	0.6	1.1	47	0.01	0.044
L100W 93 50N	Soil	2.3	84.3	195.1	294	2.2	7.4	10.8	1242	3.84	69.6	1.8	20.6	0.6	7	0.5	2.3	2.3	44	0.03	0.155
L100W 94 00N	Soil	3.1	97.6	292.6	337	1.5	13.6	14.2	1823	5.44	128.4	1.6	45.5	1.3	8	0.5	2.8	4.0	47	0.04	0.144
L100W 94 50N	Soil	2.3	103.1	222.6	381	0.7	12.7	9.2	1073	4.84	135.1	1.4	25.9	0.5	9	0.3	2.7	5.8	67	0.02	0.081
L100W 95 00N	Soil	2.3	74.9	235.8	297	1.6	15.4	15.5	1772	5.40	89.2	1.1	31.5	0.8	11	0.7	2.5	5.7	67	0.06	0.141
L100W 95 50N	Soil	1.6	61.4	134.9	189	1.3	13.4	8.3	639	4.38	50.8	1.2	15.9	0.6	14	0.5	1.9	1.9	71	0.08	0.161
L100W 96 00N	Soil	1.9	120.4	91.2	133	1.9	16.5	11.7	1161	4.90	45.1	2.0	8.8	0.2	17	0.5	2.4	0.6	90	0.08	0.105
L100W 96 50N	Soil	2.9	74.8	97.2	134	1.6	9.1	5.7	327	4.56	44.8	1.2	19.4	0.2	15	0.7	1.9	2.0	95	0.05	0.095
L100W 97 00N	Soil	2.1	47.5	31.4	93	0.8	12.6	7.5	479	4.85	36.4	1.0	6.1	0.2	16	0.3	1.9	0.5	87	0.03	0.074
L100W 97 50N	Soil	1.8	50.9	31.9	156	0.8	17.5	9.7	917	3.63	35.5	1.5	3.5	0.3	26	0.4	1.5	0.5	83	0.23	0.085
L100W 98 50N	Soil	2.1	34.5	25.5	100	0.5	14.3	6.8	275	4.18	33.7	1.0	4.8	1.7	10	0.1	1.5	0.6	80	0.02	0.046
L100W 99 00N	Soil	2.3	23.2	33.8	72	0.2	6.3	5.3	525	4.25	36.9	1.2	2.3	0.3	8	0.2	1.7	0.7	84	0.02	0.104



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

ACME ANALYTICAL LABORATORIES LTD.

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.
Vancouver BC V6C 1Z7 Canada

Project:

Zymo

Report Date:

October 03, 2008

Page:

2 of 3

Part 2

CERTIFICATE OF ANALYSIS

SMI08000894.1

Method	Analyte	Unit	MDL	1DX15 La ppm	1DX15 Cr ppm	1DX15 Mg %	1DX15 Ba ppm	1DX15 Ti %	1DX15 B ppm	1DX15 Al %	1DX15 Na %	1DX15 K %	1DX15 W ppm	1DX15 Hg ppm	1DX15 Sc ppm	1DX15 Ti ppm	1DX15 S %	1DX15 Ga ppm	1DX15 Se ppm
L98W	93 50N	Soil		10	14	0.10	94	0.005	2	1.36	0.004	0.07	<0.1	0.39	0.8	0.5	<0.05	5	1.1
L98W	94 00N	Soil		10	14	0.14	72	0.005	<1	1.49	0.004	0.06	0.2	0.10	1.7	0.3	<0.05	4	1.2
L98W	94 50N	Soil		9	13	0.04	57	0.009	2	0.65	0.003	0.05	<0.1	0.04	0.7	0.3	<0.05	6	<0.5
L98W	95 00N	Soil		14	19	0.20	116	0.005	<1	1.96	0.006	0.09	0.2	0.17	2.2	0.3	<0.05	8	0.7
L98W	95 50N	Soil		9	20	0.22	81	0.009	3	1.93	0.004	0.06	0.2	0.12	2.2	0.3	<0.05	8	0.9
L98W	96 00N	Soil		6	22	0.21	72	0.006	2	2.01	0.005	0.05	0.1	0.15	2.4	0.3	<0.05	6	1.0
L98W	96 50N	Soil		6	17	0.12	63	0.009	2	1.36	0.004	0.04	0.1	0.08	1.4	0.3	<0.05	7	<0.5
L98W	97 00N	Soil		6	19	0.20	77	0.008	1	1.53	0.005	0.06	0.1	0.09	0.8	0.2	<0.05	10	0.6
L98W	97 50N	Soil		4	18	0.20	49	0.014	1	1.49	0.004	0.04	0.2	0.11	1.4	0.1	<0.05	11	0.5
L98W	98 50N	Soil		5	19	0.12	55	0.011	<1	1.31	0.004	0.05	0.1	0.04	1.3	0.3	<0.05	8	<0.5
L98W	99 00N	Soil		8	13	0.07	46	0.006	<1	1.33	0.004	0.03	0.1	0.07	1.4	0.4	<0.05	7	0.5
L98W	99 50N	Soil		8	15	0.09	52	0.004	<1	1.17	0.003	0.03	<0.1	0.05	1.5	0.3	<0.05	5	1.5
L98W	100 00N	Soil		30	3	0.03	43	0.001	<1	1.35	0.004	0.03	0.2	0.06	0.6	0.7	<0.05	4	0.7
L98W	100 50N	Soil		15	8	0.06	69	0.003	<1	1.19	0.003	0.04	<0.1	0.06	0.7	0.5	<0.05	5	1.0
L98W	101 00N	Soil		12	19	0.29	181	0.007	3	1.86	0.006	0.07	0.2	0.11	1.3	0.2	<0.05	5	1.3
L98W	101 50N	Soil		12	8	0.04	46	0.006	<1	1.20	0.002	0.03	0.2	0.06	0.7	0.4	<0.05	7	0.9
L98W	102 00N	Soil		6	19	0.25	81	0.007	1	1.74	0.005	0.05	0.1	0.08	1.8	0.2	<0.05	6	0.7
L98W	102 50N	Soil		14	11	0.09	56	0.012	1	1.66	0.004	0.04	0.2	0.05	1.3	0.4	<0.05	9	0.7
L98W	103 00N	Soil		9	10	0.04	34	0.005	3	0.73	0.003	0.06	<0.1	0.01	0.7	0.3	<0.05	6	<0.5
L100W	93 50N	Soil		14	9	0.06	57	0.005	1	0.84	0.003	0.07	<0.1	0.08	1.3	0.2	<0.05	3	1.6
L100W	94 00N	Soil		12	12	0.13	55	0.004	<1	1.07	0.003	0.08	<0.1	0.10	1.4	0.3	<0.05	4	1.8
L100W	94 50N	Soil		13	14	0.07	77	0.007	1	0.97	0.004	0.07	<0.1	0.04	1.6	0.4	<0.05	5	1.4
L100W	95 00N	Soil		10	17	0.17	90	0.008	3	1.47	0.004	0.09	0.1	0.08	1.7	0.4	<0.05	6	1.0
L100W	95 50N	Soil		10	17	0.24	109	0.013	3	1.45	0.005	0.09	0.1	0.10	1.7	0.3	<0.05	6	1.1
L100W	96 00N	Soil		8	23	0.22	107	0.013	3	1.73	0.005	0.10	0.2	0.11	1.4	0.3	<0.05	8	1.3
L100W	96 50N	Soil		10	17	0.15	114	0.009	2	1.43	0.004	0.10	<0.1	0.09	0.9	0.4	<0.05	9	0.9
L100W	97 00N	Soil		8	19	0.20	70	0.012	2	1.80	0.004	0.06	<0.1	0.11	2.3	0.2	<0.05	8	1.1
L100W	97 50N	Soil		17	24	0.25	205	0.010	3	2.25	0.006	0.09	<0.1	0.10	2.5	0.3	<0.05	8	1.5
L100W	98 50N	Soil		7	23	0.24	66	0.011	2	2.52	0.004	0.06	0.2	0.09	3.1	0.2	<0.05	10	0.9
L100W	99 00N	Soil		12	12	0.06	52	0.009	2	1.01	0.004	0.05	<0.1	0.20	1.0	0.4	<0.05	6	<0.5



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
 Report Date: October 03, 2008

Page: 3 of 3 Part 1

CERTIFICATE OF ANALYSIS

SMI08000894.1

Method	Analyte	Unit	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
			Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	P
		MDL	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	%	
L100W	99 50N	Soil	2.4	37.6	50.8	106	0.2	8.7	6.2	518	4.13	51.0	1.4	31.7	1.1	7	0.2	2.7	3.6	70	<0.01	0.050
L100W	100 00N	Soil	1.2	15.1	47.7	18	0.4	2.5	1.1	65	1.59	20.9	0.5	11.1	0.2	6	<0.1	0.8	0.9	34	<0.01	0.027
L100W	100 50N	Soil	2.2	21.8	90.6	85	1.1	7.6	4.0	200	4.81	40.1	0.9	4.7	1.3	5	0.3	1.7	1.6	82	<0.01	0.045
L100W	101 50N	Soil	1.9	19.8	24.2	273	0.2	38.0	6.5	550	5.06	123.4	0.5	<0.5	0.3	5	0.3	1.4	1.8	75	0.03	0.075
L100W	102 00N	Soil	2.2	23.4	74.8	77	0.2	8.7	4.3	298	5.59	40.9	0.9	2.3	0.9	6	0.4	1.8	1.3	87	<0.01	0.054
L100W	102 50N	Soil	1.4	18.5	33.4	54	0.4	7.2	3.4	416	3.17	23.9	0.6	9.9	1.0	8	<0.1	1.4	0.6	65	0.01	0.046
L100W	103 00N	Soil	2.2	27.8	44.4	123	0.7	8.8	7.3	775	4.27	45.6	1.7	6.2	0.5	8	0.6	1.8	1.1	80	0.04	0.071
L110W	82 50N	Soil	0.6	4.3	4.8	20	0.2	1.4	0.7	42	0.55	5.0	0.3	9.4	0.5	8	<0.1	0.3	0.2	16	0.02	0.013
L110W	83 00N	Soil	2.4	34.3	94.3	211	1.4	10.3	11.2	1178	6.84	56.8	1.1	13.6	2.3	8	1.0	2.1	0.8	70	0.04	0.089
L110W	83 50N	Soil	15.5	88.9	671.1	443	4.6	9.5	14.1	7058	5.13	531.9	1.4	343.9	1.3	10	2.6	26.3	4.3	43	0.07	0.159
L110W	84 50N	Soil	2.1	57.1	125.2	344	1.0	13.3	13.1	997	5.41	58.5	1.5	12.8	3.8	11	1.0	2.0	1.1	60	0.04	0.084
L110W	85 00N	Soil	1.6	54.3	116.2	252	0.4	16.2	10.7	473	4.44	39.7	1.0	5.0	3.3	11	0.4	2.1	0.5	72	0.04	0.057
L110W	85 50N	Soil	1.8	13.0	14.5	70	0.8	4.5	3.6	176	2.40	24.1	0.4	1.7	1.2	5	0.1	1.6	0.2	66	<0.01	0.017
L110W	86 50N	Soil	2.1	41.9	69.6	285	0.3	18.5	15.3	583	4.52	78.2	1.2	15.8	3.4	15	0.7	2.6	0.8	74	0.05	0.049



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.

Vancouver BC V6C 1Z7 Canada

Project:

Zymo

Report Date:

October 03, 2008

Page:

3 of 3

Part 2

CERTIFICATE OF ANALYSIS

SMI08000894.1

Method	Analyte	Unit	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
			La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
			ppm	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	
		MDL	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.05	1	0.5	
L100W	99 50N	Soil	11	15	0.10	45	0.012	2	1.39	0.004	0.06	0.2	0.08	1.9	0.4	<0.05	5	0.6
L100W	100 00N	Soil	9	8	0.05	36	0.008	1	1.12	0.004	0.03	<0.1	0.06	0.6	0.4	<0.05	6	<0.5
L100W	100 50N	Soil	8	15	0.06	40	0.013	1	1.59	0.003	0.03	0.2	0.10	1.8	0.3	<0.05	9	0.6
L100W	101 50N	Soil	11	22	0.05	62	0.006	1	0.74	0.003	0.04	0.2	0.03	1.4	0.4	<0.05	5	<0.5
L100W	102 00N	Soil	6	18	0.16	54	0.012	1	1.81	0.004	0.05	0.2	0.06	1.8	0.3	<0.05	9	1.0
L100W	102 50N	Soil	5	20	0.13	45	0.009	<1	1.68	0.004	0.03	0.2	0.09	1.9	0.3	<0.05	7	0.9
L100W	103 00N	Soil	6	18	0.15	62	0.007	1	1.81	0.005	0.05	0.2	0.09	2.0	0.2	<0.05	8	0.7
L110W	82 50N	Soil	5	3	0.03	28	0.007	1	0.38	0.004	0.02	<0.1	0.04	1.0	0.1	<0.05	4	<0.5
L110W	83 00N	Soil	6	20	0.16	88	0.012	1	2.94	0.005	0.02	0.2	0.22	3.0	0.2	<0.05	5	0.7
L110W	83 50N	Soil	11	11	0.09	163	0.004	2	1.45	0.005	0.05	0.6	0.51	4.2	0.6	<0.05	4	0.6
L110W	84 50N	Soil	8	20	0.19	125	0.006	<1	3.09	0.011	0.04	0.1	0.23	3.6	0.2	<0.05	5	1.2
L110W	85 00N	Soil	7	21	0.22	126	0.007	2	3.22	0.007	0.04	0.2	0.12	4.4	0.2	<0.05	5	0.6
L110W	85 50N	Soil	7	7	0.03	40	0.006	<1	0.76	0.004	0.02	0.2	0.05	2.2	<0.1	<0.05	5	<0.5
L110W	86 50N	Soil	8	20	0.29	161	0.009	1	2.53	0.006	0.04	0.2	0.14	4.6	0.2	<0.05	4	0.5

QUALITY CONTROL REPORT

SMI08000894.1

Method	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
Analyte	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	P	
Unit	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	%	
MDL	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	0.001	
Pulp Duplicates																					
L100W 94 00N	Soil	3.1	97.6	292.6	337	1.5	13.6	14.2	1823	5.44	128.4	1.6	45.5	1.3	8	0.5	2.8	4.0	47	0.04	0.144
REP L100W 94 00N	QC	2.9	102.1	300.6	358	1.5	14.0	14.0	1905	5.50	133.2	1.5	42.5	1.3	8	0.4	3.0	4.2	48	0.04	0.154
L100W 102 50N	Soil	1.4	18.5	33.4	54	0.4	7.2	3.4	416	3.17	23.9	0.6	9.9	1.0	8	<0.1	1.4	0.6	65	0.01	0.046
REP L100W 102 50N	QC	1.5	17.3	34.0	52	0.4	8.3	3.7	414	3.14	24.5	0.6	8.3	1.1	8	0.2	1.5	0.6	68	0.01	0.047
Reference Materials																					
STD DS7	Standard	21.5	120.9	72.1	419	0.9	62.2	10.4	667	2.49	50.7	5.0	70.8	4.3	75	6.0	5.9	4.4	96	0.92	0.074
STD DS7	Standard	19.2	122.4	69.3	422	0.9	60.0	9.9	673	2.51	53.8	4.7	69.4	4.1	76	6.5	6.2	4.7	89	0.99	0.077
STD DS7 Expected		20.9	109	70.6	411	0.9	56	9.7	627	2.39	48.2	4.9	70	4.4	69	6.4	5.9	4.5	86	0.93	0.08
BLK	Blank	<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	0.02	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01	<0.001
BLK	Blank	<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01	<0.001

QUALITY CONTROL REPORT

SMI08000894.1

Method	Analyte	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
		La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
Unit		ppm	ppm	%	ppm	%	ppm	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
MDL		1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.05	1	0.5	
Pulp Duplicates																	
L100W 94 00N	Soil	12	12	0.13	55	0.004	<1	1.07	0.003	0.08	<0.1	0.10	1.4	0.3	<0.05	4	1.8
REP L100W 94 00N	QC	13	13	0.13	57	0.005	1	1.16	0.004	0.08	0.1	0.11	1.5	0.4	<0.05	4	1.5
L100W 102 50N	Soil	5	20	0.13	45	0.009	<1	1.68	0.004	0.03	0.2	0.09	1.9	0.3	<0.05	7	0.9
REP L100W 102 50N	QC	5	22	0.13	46	0.008	<1	1.74	0.004	0.04	0.2	0.10	2.3	0.3	<0.05	8	0.5
Reference Materials																	
STD DS7	Standard	13	222	1.06	399	0.131	43	1.03	0.083	0.46	3.9	0.20	2.3	4.5	0.20	5	3.3
STD DS7	Standard	11	205	1.06	377	0.120	37	1.04	0.101	0.49	3.8	0.19	3.3	4.1	0.11	5	3.3
STD DS7 Expected		13	163	1.05	370	0.124	39	0.959	0.073	0.44	3.8	0.2	2.5	4.2	0.21	5	3.5
BLK	Blank	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
BLK	Blank	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.

Vancouver BC V6C 1Z7 Canada

Submitted By:

Glen Garratt

Receiving Lab:

Canada-Smithers

Received:

September 09, 2008

Report Date:

September 30, 2008

Page:

1 of 2

CERTIFICATE OF ANALYSIS

SMI08000895.1

CLIENT JOB INFORMATION

Project: Zymo
Shipment ID: zy-rk-08-17
P.O. Number
Number of Samples: 13

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
DISP-RJT Dispose of Reject After 90 days

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Mincord Exploration Consultants Ltd.
110 - 325 Howe St.
Vancouver BC V6C 1Z7
Canada

CC: Bob Johnston

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status
R150	13	Crush, split and pulverize rock to 200 mesh		
1DX15	13	1:1:1 Aqua Regia digestion ICP-MS analysis	15	Completed

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only. All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**

110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo

Report Date: September 30, 2008

Page: 2 of 2 Part 1

CERTIFICATE OF ANALYSIS

SMI08000895.1

Method	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
Unit	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	
MDL	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	
726794	Rock	2.11	73.1	167.8	6.5	27	0.5	2.3	4.2	269	7.90	1.1	0.2	2.9	1.5	6	<0.1	0.4	1.6	59	0.04
726795	Rock	2.11	3.2	55.5	19.3	57	0.1	3.2	12.6	628	3.66	3.6	1.1	1.8	3.6	88	0.2	0.2	<0.1	98	1.50
726796	Rock	1.96	2.8	139.0	7.9	68	0.3	3.1	3.7	365	2.09	3.9	0.2	7.4	1.0	5	0.2	0.5	0.3	25	0.08
726797	Rock	2.79	6.9	67.8	49.1	83	0.3	7.5	21.1	927	8.43	20.7	<0.1	5.9	0.7	9	0.2	0.5	1.9	69	0.27
726798	Rock	2.63	3.3	145.5	21.8	43	0.2	9.2	21.4	548	10.98	7.8	0.3	5.2	0.6	11	0.1	0.3	1.2	109	0.64
726799	Rock	2.59	3.0	242.5	10.3	70	0.3	14.1	16.6	746	6.94	2.5	0.1	7.1	0.7	93	0.2	0.4	0.3	142	1.55
726800	Rock	3.56	1.9	1654	6.0	45	2.0	5.8	20.3	427	7.09	1.5	0.5	142.4	2.0	77	<0.1	0.2	0.5	179	1.76
726801	Rock	2.09	5.9	1042	4.3	37	0.8	4.3	14.4	367	6.10	1.9	0.5	82.6	3.2	90	0.1	0.2	0.2	120	1.32
726802	Rock	2.46	3.3	127.8	4.1	27	0.2	3.6	13.4	296	3.32	2.3	0.8	11.1	3.6	101	<0.1	<0.1	0.4	68	1.72
726803	Rock	2.06	2.6	1918	6.4	36	0.9	4.9	6.7	258	8.43	4.2	1.5	193.5	5.9	41	0.2	<0.1	0.2	140	0.31
726804	Rock	2.13	0.6	23.4	22.1	68	0.2	8.8	7.6	627	4.19	1.7	<0.1	207.6	0.8	17	0.2	0.8	1.9	47	0.88
726805	Rock	2.15	0.4	17.5	9.3	48	<0.1	6.4	8.7	513	3.77	31.6	<0.1	9.6	0.4	39	0.2	2.7	1.1	21	1.02
726806	Rock	1.99	1.8	34.0	20.2	86	<0.1	6.9	5.6	654	3.49	9.2	0.1	2.7	1.1	11	0.2	0.8	0.5	43	0.42



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
Report Date: September 30, 2008

Page: 2 of 2 **Part** 2

CERTIFICATE OF ANALYSIS

SMI08000895.1

Method	Analyte	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
		P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
Unit		%	ppm	ppm	%	ppm	%	ppm	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
MDL		0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.05	1	0.5	
726794	Rock	0.084	8	9	0.28	113	0.001	2	0.79	0.023	0.21	0.1	0.03	5.1	0.3	0.34	3	4.6
726795	Rock	0.141	13	3	0.90	61	0.129	3	2.14	0.146	0.10	0.4	<0.01	3.4	<0.1	0.54	7	<0.5
726796	Rock	0.037	11	5	0.32	48	0.001	<1	0.85	0.019	0.20	0.2	0.01	3.8	0.3	0.05	3	<0.5
726797	Rock	0.070	5	15	0.99	54	0.003	1	1.92	0.019	0.19	0.1	0.02	6.2	0.2	1.94	6	1.4
726798	Rock	0.271	5	23	1.09	16	0.034	1	2.40	0.025	0.21	0.3	0.01	7.6	0.2	5.17	9	6.2
726799	Rock	0.068	6	32	1.70	44	0.106	2	4.24	0.383	0.16	<0.1	0.02	9.2	0.2	2.55	11	1.3
726800	Rock	0.109	6	4	1.25	45	0.239	3	2.47	0.109	0.19	0.5	0.02	3.5	0.2	0.86	10	0.8
726801	Rock	0.150	7	5	1.41	54	0.152	2	2.21	0.134	0.23	0.2	0.01	4.7	0.2	0.72	10	0.8
726802	Rock	0.176	9	4	0.82	45	0.127	2	2.15	0.151	0.12	0.4	<0.01	1.5	0.1	1.31	7	0.6
726803	Rock	0.118	9	11	0.15	288	0.003	1	0.41	0.029	0.17	<0.1	0.35	3.5	<0.1	0.35	6	1.9
726804	Rock	0.109	9	12	0.57	150	0.004	<1	1.14	0.013	0.25	<0.1	<0.01	5.0	0.2	0.90	4	0.7
726805	Rock	0.125	5	3	0.24	81	0.001	1	0.39	0.029	0.14	0.2	0.01	5.7	0.2	0.96	1	<0.5
726806	Rock	0.054	7	13	0.69	105	0.002	2	1.21	0.030	0.16	<0.1	0.01	5.2	0.1	0.33	5	<0.5

QUALITY CONTROL REPORT

SMI08000895.1

Method	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
Unit	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	
MDL	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	
Pulp Duplicates																					
726804	Rock	2.13	0.6	23.4	22.1	68	0.2	8.8	7.6	627	4.19	1.7	<0.1	207.6	0.8	17	0.2	0.8	1.9	47	0.88
REP 726804	QC		0.6	26.5	23.0	70	0.2	8.4	7.6	644	4.31	1.6	<0.1	211.2	0.8	17	0.2	0.8	2.0	48	0.89
Reference Materials																					
STD DS7	Standard		20.4	103.9	71.8	405	0.9	56.3	9.3	629	2.45	48.8	4.8	71.6	4.4	71	6.0	5.8	4.2	90	0.96
STD DS7	Standard		20.8	113.0	75.6	428	0.9	62.5	9.5	676	2.53	50.7	5.0	67.2	4.5	77	6.1	6.0	4.4	92	1.03
STD DS7 Expected			20.9	109	70.6	411	0.9	56	9.7	627	2.39	48.2	4.9	70	4.4	69	6.4	5.9	4.5	86	0.93
BLK	Blank		<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01
Prep Wash																					
G1	Prep Blank	<0.01	0.8	2.2	2.6	50	<0.1	4.9	4.8	593	2.09	<0.5	2.0	1.3	4.1	57	<0.1	<0.1	0.2	42	0.56
G1	Prep Blank	<0.01	0.6	2.0	2.6	47	<0.1	4.9	4.9	599	2.16	<0.5	2.2	<0.5	4.3	71	<0.1	<0.1	<0.1	44	0.66

QUALITY CONTROL REPORT

SMI08000895.1

Method		1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte		P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
Unit		%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm
MDL		0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5
Pulp Duplicates																		
726804	Rock	0.109	9	12	0.57	150	0.004	<1	1.14	0.013	0.25	<0.1	<0.01	5.0	0.2	0.90	4	0.7
REP 726804	QC	0.109	10	12	0.59	163	0.004	1	1.18	0.014	0.25	<0.1	<0.01	5.2	0.2	0.92	4	0.7
Reference Materials																		
STD DS7	Standard	0.075	12	204	1.09	381	0.119	40	1.04	0.091	0.45	3.8	0.21	2.1	4.5	0.20	5	3.6
STD DS7	Standard	0.074	14	217	1.10	410	0.128	43	1.09	0.095	0.47	4.1	0.20	2.4	4.6	0.20	5	3.8
STD DS7 Expected		0.08	13	163	1.05	370	0.124	39	0.959	0.073	0.44	3.8	0.2	2.5	4.2	0.21	4.6	3.5
BLK	Blank	<0.001	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
Prep Wash																		
G1	Prep Blank	0.084	7	11	0.65	245	0.138	1	1.00	0.065	0.52	2.0	<0.01	1.8	0.4	<0.05	5	<0.5
G1	Prep Blank	0.080	8	12	0.65	235	0.145	<1	1.06	0.086	0.53	1.5	<0.01	2.0	0.4	<0.05	5	<0.5



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.

Vancouver BC V6C 1Z7 Canada

Submitted By:

Glen Garratt

Receiving Lab:

Canada-Smithers

Received:

September 09, 2008

Report Date:

October 17, 2008

Page:

1 of 2

CERTIFICATE OF ANALYSIS

SMI08000896.1

CLIENT JOB INFORMATION

Project: Zymo
Shipment ID: zy-co-08-01
P.O. Number
Number of Samples: 15

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status
R150	15	Crush split and pulverize drill core to 200 mesh		
1DX15	15	1:1:1 Aqua Regia digestion ICP-MS analysis	15	Completed

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
DISP-RJT Dispose of Reject After 90 days

ADDITIONAL COMMENTS

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Mincord Exploration Consultants Ltd.
110 - 325 Howe St.
Vancouver BC V6C 1Z7
Canada

CC: Bob Johnston



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only. All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.

** asterisk indicates that an analytical result could not be provided due to unusually high levels of interference from other elements.



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**

110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo

Report Date: October 17, 2008

Page: 2 of 2 Part 1

CERTIFICATE OF ANALYSIS

SMI08000896.1

Method Analyte Unit MDL	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	ppm	
	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01
933001	Drill Core	2.75	76.6	1832	9.5	36	0.6	2.1	6.7	427	2.83	2.3	6.1	137.9	16.5	731	0.2	1.2	0.2	64	1.65
933002	Drill Core	6.99	128.0	1103	11.6	24	0.5	1.7	6.4	482	2.50	13.0	7.1	53.1	17.8	208	0.2	4.0	0.2	26	2.45
933003	Drill Core	6.82	1.7	591.2	6.3	27	0.2	1.8	6.4	323	2.81	2.3	5.6	36.2	21.4	2265	0.1	0.6	<0.1	53	1.67
933004	Drill Core	7.13	32.1	890.5	5.6	25	0.4	1.6	5.9	356	2.59	2.0	5.2	50.2	19.3	442	0.1	0.6	0.1	48	2.84
933005	Drill Core	7.06	2.6	868.5	6.0	28	0.3	1.9	6.6	275	2.84	1.5	5.1	46.2	21.4	850	<0.1	0.2	<0.1	76	1.63
933006	Drill Core	6.83	2.4	789.8	6.6	38	0.3	2.2	6.6	279	2.76	0.9	3.9	47.6	21.6	158	<0.1	<0.1	<0.1	75	1.30
933007	Drill Core	7.27	7.1	1285	11.7	38	0.4	1.7	6.6	559	2.55	6.9	6.1	72.7	18.4	1103	0.1	1.0	<0.1	32	2.38
933008	Drill Core	7.67	19.7	1717	8.6	31	0.5	1.8	7.5	851	2.82	10.4	7.5	110.5	16.6	421	<0.1	4.6	0.1	27	3.60
933009	Drill Core	7.49	9.4	1049	6.8	35	0.3	2.3	6.6	302	2.85	1.3	5.9	65.4	20.3	412	0.1	0.1	<0.1	73	1.44
933010	Drill Core	8.03	1.9	1662	8.7	46	0.5	2.4	8.6	417	3.52	1.0	4.7	111.0	19.3	383	0.2	<0.1	<0.1	72	1.72
933011	Drill Core	7.00	6.4	2065	7.9	40	0.6	2.7	8.4	589	3.45	5.2	5.7	128.4	19.5	456	0.1	3.3	0.1	54	2.31
933012	Drill Core	8.22	1.6	1285	12.6	56	0.4	2.4	8.4	577	3.46	1.0	4.8	101.8	17.6	1103	0.2	0.9	0.1	76	2.19
933013	Drill Core	7.17	3.3	1329	11.1	67	0.4	2.8	9.2	779	3.71	2.9	5.1	99.2	16.9	248	0.2	2.8	0.1	79	2.53
933014	Drill Core	7.81	4.8	2039	7.7	41	0.7	2.3	7.7	524	3.23	0.9	5.8	112.5	19.6	508	0.1	0.4	0.1	78	1.71
933015	Drill Core	6.59	2.5	3251	8.5	62	1.0	3.4	9.8	570	4.26	2.0	3.8	261.8	16.8	666	0.3	0.5	0.2	76	1.97



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
Report Date: October 17, 2008

Page: 2 of 2 **Part** 2

CERTIFICATE OF ANALYSIS

SMI08000896.1

Method	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se	
Unit	%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
MDL	0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5	
933001	Drill Core	0.112	26	6	0.56	410	0.028	2	0.59	0.043	0.17	0.3	0.28	3.2	<0.1	0.34	4	1.4
933002	Drill Core	0.128	18	3	0.54	302	<0.001	3	0.29	0.009	0.23	<0.1	0.27	3.8	0.2	0.35	<1	1.1
933003	Drill Core	0.127	24	5	0.62	410	0.014	2	0.56	0.028	0.20	<0.1	0.19	3.6	0.1	0.28	3	0.7
933004	Drill Core	0.125	24	5	0.60	334	0.005	2	0.61	0.017	0.18	<0.1	0.24	3.3	0.1	0.32	3	<0.5
933005	Drill Core	0.131	26	7	0.71	265	0.026	<1	0.81	0.041	0.15	0.1	0.25	3.3	<0.1	0.23	5	0.8
933006	Drill Core	0.125	25	7	0.69	149	0.046	1	0.78	0.042	0.15	<0.1	0.11	3.4	<0.1	0.14	5	0.6
933007	Drill Core	0.122	20	4	0.58	171	0.002	2	0.45	0.019	0.23	<0.1	0.68	3.0	0.1	0.76	2	1.2
933008	Drill Core	0.101	21	4	0.94	186	0.002	1	0.36	0.015	0.21	<0.1	0.29	2.9	0.1	0.67	2	1.5
933009	Drill Core	0.122	27	6	0.66	166	0.035	1	0.75	0.038	0.14	<0.1	0.11	3.1	<0.1	0.22	5	1.2
933010	Drill Core	0.116	24	6	0.68	272	0.031	<1	0.75	0.030	0.16	<0.1	0.16	3.4	<0.1	0.33	5	0.7
933011	Drill Core	0.116	21	7	0.63	314	0.004	3	0.75	0.025	0.23	<0.1	0.12	2.6	0.1	0.44	4	1.2
933012	Drill Core	0.128	25	7	0.69	522	0.012	1	0.80	0.031	0.17	<0.1	0.12	3.3	<0.1	0.27	5	<0.5
933013	Drill Core	0.127	27	6	0.77	379	0.007	1	0.95	0.025	0.17	<0.1	0.22	3.3	0.1	0.34	5	0.7
933014	Drill Core	0.108	24	7	0.56	297	0.022	2	0.73	0.028	0.14	<0.1	0.11	2.5	<0.1	0.35	4	1.1
933015	Drill Core	0.129	22	8	0.69	262	0.011	2	0.72	0.030	0.19	<0.1	0.16	3.4	<0.1	0.55	4	1.2

QUALITY CONTROL REPORT

SMI08000896.1

Method	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
Unit	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	
MDL	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	
Pulp Duplicates																					
933008	Drill Core	7.67	19.7	1717	8.6	31	0.5	1.8	7.5	851	2.82	10.4	7.5	110.5	16.6	421	<0.1	4.6	0.1	27	3.60
REP 933008	QC		20.8	1738	8.3	31	0.5	1.7	7.8	879	2.88	10.5	7.5	109.9	17.2	429	0.2	5.1	0.1	28	3.76
Reference Materials																					
STD DS7	Standard		20.4	103.9	71.8	405	0.9	56.3	9.3	629	2.45	48.8	4.8	71.6	4.4	71	6.0	5.8	4.2	90	0.96
STD DS7	Standard		20.8	113.0	75.6	428	0.9	62.5	9.5	676	2.53	50.7	5.0	67.2	4.5	77	6.1	6.0	4.4	92	1.03
STD DS7	Standard		20.0	109.0	74.8	394	0.9	55.4	9.0	629	2.38	50.7	5.2	73.7	4.7	71	5.8	5.7	4.7	85	0.92
STD DS7	Standard		20.6	103.4	66.8	411	0.9	51.6	9.0	652	2.42	51.5	5.4	63.4	4.8	79	6.8	6.2	4.7	90	0.98
STD DS7	Standard		18.4	97.1	63.2	391	0.9	48.2	8.7	638	2.40	50.1	5.0	65.9	4.4	76	6.5	5.8	4.5	90	0.97
STD DS7	Standard		20.9	110.5	72.3	407	0.8	55.7	9.7	647	2.48	52.7	5.0	66.4	4.7	77	6.4	6.2	4.9	84	0.98
STD DS7	Standard		21.5	115.8	73.3	443	0.9	58.0	9.6	680	2.59	57.1	5.0	72.0	4.7	77	6.7	6.6	5.1	86	1.00
STD DS7 Expected			20.9	109	70.6	411	0.9	56	9.7	627	2.39	48.2	4.9	70	4.4	69	6.4	5.9	4.5	86	0.93
BLK	Blank		<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01
BLK	Blank		<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01
BLK	Blank		<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	0.02	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01
BLK	Blank		<0.1	1.5	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01
Prep Wash																					
G1	Prep Blank	<0.01	0.2	2.4	2.6	48	<0.1	4.5	4.6	582	2.09	<0.5	2.0	<0.5	3.9	59	<0.1	<0.1	<0.1	43	0.60
G1	Prep Blank	<0.01	0.2	2.7	2.4	46	<0.1	3.6	4.8	586	2.07	<0.5	2.0	<0.5	4.4	58	<0.1	<0.1	<0.1	43	0.56

QUALITY CONTROL REPORT

SMI08000896.1

Method		1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte		P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
Unit		%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm
MDL		0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5
Pulp Duplicates																		
933008	Drill Core	0.101	21	4	0.94	186	0.002	1	0.36	0.015	0.21	<0.1	0.29	2.9	0.1	0.67	2	1.5
REP 933008	QC	0.106	22	5	0.97	175	0.002	1	0.35	0.016	0.21	<0.1	0.29	2.9	0.1	0.69	1	1.4
Reference Materials																		
STD DS7	Standard	0.075	12	204	1.09	381	0.119	40	1.04	0.091	0.45	3.8	0.21	2.1	4.5	0.20	5	3.6
STD DS7	Standard	0.074	14	217	1.10	410	0.128	43	1.09	0.095	0.47	4.1	0.20	2.4	4.6	0.20	5	3.8
STD DS7	Standard	0.074	12	191	1.04	393	0.114	41	1.01	0.084	0.45	3.7	0.20	2.3	4.5	0.19	5	3.3
STD DS7	Standard	0.079	14	193	1.07	432	0.124	38	1.07	0.096	0.48	4.1	0.21	2.8	4.4	0.19	5	3.7
STD DS7	Standard	0.078	13	187	1.04	404	0.115	37	1.02	0.091	0.46	4.0	0.20	2.5	4.1	0.19	5	3.6
STD DS7	Standard	0.078	14	202	1.05	401	0.126	39	1.06	0.087	0.46	4.0	0.23	2.4	4.4	0.20	5	4.1
STD DS7	Standard	0.085	14	208	1.10	416	0.127	42	1.05	0.089	0.51	3.9	0.21	2.6	4.5	0.21	5	3.2
STD DS7 Expected		0.08	13	163	1.05	370	0.124	39	0.959	0.073	0.44	3.8	0.2	2.5	4.2	0.21	4.6	3.5
BLK	Blank	<0.001	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
BLK	Blank	<0.001	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
BLK	Blank	<0.001	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
BLK	Blank	<0.001	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
Prep Wash																		
G1	Prep Blank	0.080	6	9	0.65	226	0.135	<1	1.01	0.066	0.51	<0.1	<0.01	1.9	0.4	<0.05	5	<0.5
G1	Prep Blank	0.080	7	10	0.63	228	0.133	2	0.97	0.059	0.52	0.2	<0.01	1.8	0.4	<0.05	5	<0.5



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.

Vancouver BC V6C 1Z7 Canada

Submitted By:

Glen Garratt

Receiving Lab:

Canada-Smithers

Received:

September 16, 2008

Report Date:

October 17, 2008

Page:

1 of 3

CERTIFICATE OF ANALYSIS

SMI08000932.1

CLIENT JOB INFORMATION

Project: Zymo
Shipment ID: zy-co-08-02
P.O. Number
Number of Samples: 49

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
DISP-RJT Dispose of Reject After 90 days

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Mincord Exploration Consultants Ltd.
110 - 325 Howe St.
Vancouver BC V6C 1Z7
Canada

CC: Bob Johnston

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status
R150	47	Crush split and pulverize drill core to 200 mesh		
1DX15	49	1:1:1 Aqua Regia digestion ICP-MS analysis	15	Completed

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only. All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.

** asterisk indicates that an analytical result could not be provided due to unusually high levels of interference from other elements.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

ACME ANALYTICAL LABORATORIES LTD.

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.
Vancouver BC V6C 1Z7 Canada

Project:

Zymo

Report Date:

October 17, 2008

Page:

2 of 3

Part 1

CERTIFICATE OF ANALYSIS

SMI08000932.1

Method Analyte Unit MDL	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	ppm	
	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	
933016	Drill Core	7.50	2.0	2073	13.2	63	0.6	2.5	10.0	719	4.56	8.9	3.7	149.6	14.2	418	0.2	8.0	0.1	74	2.42
933017	Drill Core	7.22	3.2	1225	8.9	41	0.5	1.7	6.9	784	3.43	58.2	3.7	68.3	13.4	145	0.3	82.9	<0.1	26	2.89
933018	Drill Core	7.08	2.2	1306	8.7	45	0.4	2.6	7.3	724	3.71	17.2	3.8	91.9	14.5	141	0.1	2.2	0.1	55	2.27
933019	Drill Core	8.34	2.5	982.0	10.7	48	0.5	2.6	7.8	1287	3.82	9.6	3.9	60.3	14.6	384	0.1	3.4	0.2	57	2.56
933020	Drill Core	7.95	5.4	1185	7.8	51	0.5	2.0	7.7	921	3.97	2.8	3.8	69.8	15.3	857	0.2	2.1	0.1	82	2.27
933021	Drill Core	8.01	8.5	1884	8.1	53	0.6	3.1	8.9	656	4.07	3.6	3.9	159.0	15.3	778	0.2	1.1	0.2	94	1.75
933022	Drill Core	9.45	2.1	1559	8.5	46	0.5	2.5	7.7	487	3.68	2.3	4.1	116.3	15.5	1301	0.2	1.6	0.1	89	1.90
933023	Drill Core	9.27	4.2	2086	11.5	40	0.6	2.3	8.1	596	3.95	14.8	4.1	131.4	15.0	442	0.3	7.6	0.2	49	2.53
933024	Drill Core	13.94	4.9	1628	9.9	35	0.6	2.4	7.1	522	3.52	14.5	3.9	141.7	15.0	277	0.2	6.3	0.2	45	2.42
933026	Drill Core	7.53	1.5	1371	9.7	47	0.6	3.3	6.8	861	4.06	83.1	3.2	89.8	12.9	134	0.2	18.5	0.1	52	2.83
933027	Drill Core	8.91	1.3	1795	6.3	40	0.7	3.4	8.6	498	5.33	6.5	3.3	130.8	14.8	759	<0.1	3.7	0.2	97	1.70
933028	Drill Core	7.26	1.6	2073	6.0	44	0.7	3.6	8.9	871	5.18	5.8	3.0	159.6	14.8	620	0.2	2.7	0.2	100	2.06
933029	Drill Core	8.32	3.2	2564	18.9	56	1.0	3.2	9.7	624	5.04	29.7	3.5	246.7	14.7	748	0.2	41.4	0.2	74	2.13
933030	Rock Pulp	0.10	5.4	2677	10.7	105	0.4	95.3	10.9	689	4.96	11.1	0.1	198.7	1.0	148	0.4	6.0	0.3	48	2.41
933031	Drill Core	7.04	17.9	1060	5.2	30	0.3	2.1	6.1	332	3.08	3.6	3.2	66.4	13.7	258	<0.1	5.0	0.1	68	1.99
933032	Drill Core	6.97	1.6	1052	6.1	31	0.4	2.7	7.4	346	3.08	3.9	4.4	88.9	16.1	1316	<0.1	1.3	0.2	69	1.69
933033	Drill Core	7.00	1.6	1262	5.0	38	0.4	2.6	7.4	399	3.69	1.6	3.7	95.9	15.0	781	<0.1	0.4	0.1	86	1.43
933034	Drill Core	7.80	2.0	1827	7.3	50	0.5	3.0	8.1	520	4.57	24.4	3.3	145.0	12.6	788	0.2	1.7	0.1	85	1.58
933035	Drill Core	7.22	1.8	1460	10.2	33	0.6	2.1	6.7	682	2.92	11.4	5.6	111.2	14.8	386	0.2	6.2	0.2	41	2.56
933036	Drill Core	7.23	1.7	1720	5.9	40	0.5	2.4	7.8	575	5.73	5.0	2.3	147.6	12.8	205	<0.1	0.6	0.1	88	1.84
933037	Drill Core	7.26	1.8	1502	8.0	39	0.5	2.2	6.6	606	4.00	23.3	2.6	111.5	12.2	154	<0.1	1.5	0.2	43	2.06
933038	Drill Core	7.27	2.0	1343	7.1	28	0.6	1.7	6.2	624	3.55	596.6	1.8	83.5	8.7	128	<0.1	3.6	0.1	34	3.27
933039	Drill Core	6.85	5.1	1719	8.3	36	0.6	2.0	7.3	944	3.74	154.9	2.0	105.3	9.6	118	<0.1	7.1	0.2	22	2.96
933040	Drill Core	7.36	4.4	2069	7.8	43	0.5	3.1	7.9	605	5.17	39.9	2.4	141.1	11.9	133	<0.1	6.8	0.1	35	2.21
933041	Drill Core	7.27	18.5	3241	14.1	54	0.9	2.8	8.2	476	4.26	52.8	2.8	214.8	12.8	118	<0.1	7.8	0.2	21	1.86
933042	Drill Core	7.21	3.3	4402	8.4	61	1.3	3.0	9.3	578	5.08	23.5	2.6	294.4	12.2	109	0.2	2.9	0.2	31	2.08
933043	Drill Core	7.07	3.8	3406	13.7	46	1.2	3.5	10.2	657	5.45	55.5	1.9	260.3	8.9	239	0.2	3.3	0.3	44	1.97
933044	Drill Core	7.37	72.7	6234	10.5	80	1.7	4.5	12.3	592	5.69	29.0	2.4	423.8	11.8	388	0.3	4.0	0.3	62	1.47
933045	Drill Core	8.24	5.3	5540	7.2	54	1.3	3.4	10.3	549	4.25	21.0	2.5	382.8	11.3	321	0.2	2.7	0.2	35	1.57
933046	Drill Core	7.28	12.7	3457	9.5	58	0.9	4.1	9.8	530	5.05	104.8	2.3	280.7	11.3	316	0.2	18.1	0.2	47	1.26

This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
 Report Date: October 17, 2008

Page: 2 of 3 Part 2

CERTIFICATE OF ANALYSIS

SMI08000932.1

Method	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se	
Unit	%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
MDL	0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5	
933016	Drill Core	0.138	25	8	0.67	313	0.016	2	0.55	0.037	0.22	0.2	0.31	3.7	<0.1	0.46	4	1.5
933017	Drill Core	0.123	21	3	0.73	335	0.001	3	0.38	0.011	0.25	0.2	0.50	4.1	<0.1	0.39	1	<0.5
933018	Drill Core	0.146	29	5	0.62	382	0.002	2	0.52	0.018	0.21	0.1	0.44	4.3	0.1	0.37	2	0.6
933019	Drill Core	0.139	29	5	0.67	438	0.005	1	0.43	0.024	0.22	0.2	0.24	4.1	0.2	0.30	2	1.0
933020	Drill Core	0.141	30	7	0.63	472	0.016	2	0.57	0.036	0.19	0.2	0.18	3.8	<0.1	0.26	4	<0.5
933021	Drill Core	0.137	27	6	0.66	216	0.032	2	0.68	0.042	0.17	0.4	0.21	3.2	<0.1	0.37	5	1.5
933022	Drill Core	0.148	28	8	0.54	399	0.034	<1	0.58	0.037	0.17	0.1	0.17	3.6	<0.1	0.30	4	0.7
933023	Drill Core	0.135	20	4	0.65	260	0.003	4	0.47	0.018	0.27	17.9	0.47	3.8	0.3	0.55	2	1.3
933024	Drill Core	0.118	17	5	0.65	217	0.003	1	0.46	0.014	0.23	0.1	0.25	3.5	0.1	0.61	2	0.6
933026	Drill Core	0.109	13	4	0.86	104	0.001	4	0.43	0.011	0.23	0.1	0.46	3.4	0.2	0.81	2	1.2
933027	Drill Core	0.103	16	9	0.53	216	0.014	2	0.45	0.029	0.21	0.1	0.29	2.7	0.2	0.65	3	<0.5
933028	Drill Core	0.097	16	7	0.59	401	0.008	2	0.52	0.030	0.22	0.4	0.20	3.2	0.1	0.42	4	1.5
933029	Drill Core	0.114	19	6	0.56	87	0.005	1	0.41	0.019	0.23	<0.1	0.30	3.0	0.1	1.42	2	2.1
933030	Rock Pulp	0.093	4	123	0.94	27	0.001	4	0.82	0.046	0.28	0.3	1.04	5.3	0.1	2.48	2	6.5
933031	Drill Core	0.107	20	5	0.56	276	0.008	2	0.56	0.028	0.16	<0.1	0.14	3.0	<0.1	0.24	4	<0.5
933032	Drill Core	0.117	23	6	0.63	192	0.013	1	0.68	0.033	0.15	<0.1	0.15	2.8	0.1	0.53	4	0.6
933033	Drill Core	0.126	23	6	0.66	191	0.022	<1	0.76	0.046	0.14	0.1	0.12	3.3	<0.1	0.37	6	0.8
933034	Drill Core	0.137	21	6	0.57	242	0.025	2	0.53	0.027	0.14	0.1	0.20	3.5	<0.1	0.35	5	1.4
933035	Drill Core	0.126	25	3	0.61	225	0.003	2	0.39	0.025	0.19	<0.1	0.28	3.4	<0.1	0.54	2	1.1
933036	Drill Core	0.111	12	6	0.61	242	0.002	2	0.52	0.029	0.17	<0.1	0.26	3.1	<0.1	0.45	5	0.8
933037	Drill Core	0.083	10	4	0.60	149	<0.001	3	0.34	0.026	0.19	<0.1	0.47	2.6	0.1	0.73	2	1.3
933038	Drill Core	0.113	12	3	0.80	142	<0.001	6	0.33	0.020	0.23	<0.1	0.61	3.6	0.5	0.43	<1	0.9
933039	Drill Core	0.094	10	3	0.69	160	<0.001	5	0.27	0.016	0.23	<0.1	0.39	2.6	0.3	0.73	<1	0.9
933040	Drill Core	0.111	11	5	0.63	214	<0.001	6	0.36	0.019	0.26	<0.1	1.17	3.1	0.2	0.61	1	0.9
933041	Drill Core	0.116	11	4	0.49	104	<0.001	5	0.30	0.018	0.24	<0.1	0.92	2.9	0.2	1.03	<1	2.4
933042	Drill Core	0.121	12	5	0.56	138	<0.001	4	0.30	0.022	0.23	0.1	0.98	2.9	0.2	0.90	1	2.6
933043	Drill Core	0.103	10	4	0.61	72	0.002	4	0.34	0.025	0.20	<0.1	1.11	3.2	0.1	1.66	3	2.5
933044	Drill Core	0.105	12	6	0.60	92	0.005	3	0.45	0.032	0.22	<0.1	0.94	2.9	0.1	1.37	4	4.6
933045	Drill Core	0.104	10	5	0.55	174	0.005	5	0.45	0.032	0.24	<0.1	0.94	2.9	0.2	0.78	3	3.6
933046	Drill Core	0.110	11	6	0.45	125	0.003	5	0.47	0.042	0.26	<0.1	1.36	2.9	0.3	0.97	3	3.0

This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**

110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo

Report Date: October 17, 2008

Page: 3 of 3 Part 1

CERTIFICATE OF ANALYSIS

SMI08000932.1

Method	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
Unit	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	
MDL	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	
933047	Drill Core	7.34	1.4	3519	8.7	68	0.9	3.6	10.8	769	6.44	195.5	2.4	283.1	13.6	257	0.2	29.4	0.2	73	1.43
933048	Drill Core	7.61	8.8	4988	12.7	50	1.7	4.0	10.6	826	4.42	64.7	2.0	355.1	9.0	144	0.2	12.8	0.2	25	2.01
933049	Drill Core	7.45	1.5	5264	9.4	47	1.2	3.4	9.9	461	4.08	42.2	2.4	429.9	11.5	856	0.2	2.8	0.2	47	1.99
933050	Drill Core	7.81	7.9	3408	7.0	43	1.0	3.4	9.0	419	4.01	30.6	3.8	261.3	14.1	798	0.2	1.8	0.2	60	1.86
933051	Drill Core	8.10	12.6	4937	8.1	36	1.5	2.9	9.3	476	4.42	22.9	2.6	311.7	12.0	491	0.1	1.7	0.4	44	2.29
933052	Drill Core	6.15	3.7	3101	5.4	34	1.0	2.7	7.9	392	4.16	13.1	3.3	244.2	11.8	860	<0.1	1.0	0.2	64	1.69
933053	Drill Core	7.28	37.6	2499	8.1	33	1.0	2.3	7.9	393	4.01	46.7	3.0	165.6	12.2	741	<0.1	18.9	0.2	55	1.85
933054	Drill Core	7.34	9.5	2199	6.8	34	0.6	2.9	7.1	487	3.88	60.7	2.6	155.1	12.3	748	<0.1	1.9	0.2	48	2.32
933055	Drill Core	8.40	19.1	2711	11.5	47	0.8	2.6	8.1	425	3.79	630.2	2.6	182.3	10.9	618	0.1	45.9	0.2	35	1.76
933056	Drill Core	7.76	15.7	1968	8.8	35	0.7	2.6	7.7	636	4.06	136.7	3.0	133.4	11.1	545	<0.1	8.8	0.2	29	2.03
933057	Drill Core	7.63	5.6	2605	8.2	29	0.9	2.5	7.5	479	3.65	26.3	3.0	141.7	10.1	871	<0.1	1.4	0.3	28	2.78
933058	Drill Core	7.18	13.2	2178	16.6	41	0.8	2.3	6.9	398	2.76	215.5	3.4	105.4	8.3	358	0.1	70.3	0.2	14	1.95
933059	Drill Core	7.69	19.4	1620	9.3	33	0.6	2.9	7.3	455	2.88	110.5	3.5	59.5	8.8	52	<0.1	31.9	0.4	14	1.08
933060	Rock Pulp	0.04	6.4	3111	12.9	118	0.5	125.8	11.9	780	5.71	14.3	0.2	231.8	1.3	177	0.5	7.3	0.4	56	2.75
933061	Drill Core	7.74	5.4	1845	11.5	38	0.6	2.9	7.4	552	3.03	865.2	3.6	122.5	9.5	74	<0.1	71.4	0.2	25	1.22
933062	Drill Core	7.79	15.3	2019	8.2	31	0.6	2.3	7.0	377	2.98	215.2	3.7	109.6	10.5	1040	0.2	8.1	0.2	25	2.10
933063	Drill Core	7.52	2.6	818.6	7.5	29	0.3	2.1	5.6	396	2.76	16.9	4.4	59.3	12.2	1028	<0.1	1.5	0.1	39	2.45
933064	Drill Core	7.26	9.3	1889	8.1	35	0.6	3.0	8.4	517	2.97	40.6	3.8	121.5	11.2	741	0.2	3.7	0.1	23	2.39
933065	Drill Core	8.35	2.7	1367	11.7	31	0.5	5.8	7.8	578	3.12	103.2	4.4	126.6	11.4	910	0.3	3.2	0.3	21	2.52



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
 Report Date: October 17, 2008

Page: 3 of 3 Part 2

CERTIFICATE OF ANALYSIS

SMI08000932.1

Method	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se	
Unit	%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
MDL	0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5	
933047	Drill Core	0.136	12	4	0.49	139	0.003	5	0.42	0.037	0.24	<0.1	1.03	3.5	0.4	0.96	4	3.0
933048	Drill Core	0.095	10	5	0.57	81	<0.001	6	0.36	0.032	0.25	0.2	0.75	2.8	0.2	1.26	1	3.8
933049	Drill Core	0.112	12	5	0.63	218	0.005	4	0.45	0.041	0.24	<0.1	1.17	3.1	0.2	0.76	3	3.4
933050	Drill Core	0.124	19	7	0.71	187	0.014	4	0.75	0.062	0.27	<0.1	0.98	3.2	0.2	0.81	4	2.2
933051	Drill Core	0.207	21	5	0.67	77	0.002	4	0.54	0.036	0.21	0.1	1.13	2.9	0.1	1.50	3	3.9
933052	Drill Core	0.125	19	7	0.66	121	0.012	2	0.75	0.048	0.21	0.2	0.59	3.0	0.1	1.15	5	1.8
933053	Drill Core	0.118	19	4	0.62	108	0.003	4	0.72	0.043	0.22	<0.1	1.34	2.7	0.1	1.24	4	1.9
933054	Drill Core	0.105	18	6	0.61	107	0.002	4	0.66	0.046	0.23	0.1	0.54	2.7	0.1	1.08	4	1.8
933055	Drill Core	0.108	15	4	0.49	63	<0.001	4	0.45	0.039	0.22	<0.1	1.94	2.4	0.2	1.74	2	2.7
933056	Drill Core	0.112	16	4	0.53	66	<0.001	5	0.44	0.044	0.27	0.4	0.99	2.9	0.3	1.55	2	2.1
933057	Drill Core	0.114	14	4	0.66	59	0.001	3	0.39	0.035	0.23	<0.1	0.79	2.6	0.2	1.39	2	1.6
933058	Drill Core	0.108	11	5	0.40	54	<0.001	5	0.36	0.030	0.24	<0.1	1.63	2.0	0.2	1.45	<1	2.3
933059	Drill Core	0.123	11	3	0.23	43	<0.001	4	0.43	0.045	0.27	0.2	1.97	2.0	0.2	2.12	1	1.8
933060	Rock Pulp	0.107	5	153	1.11	35	0.001	5	1.02	0.055	0.33	0.4	1.20	6.1	0.2	2.82	3	7.7
933061	Drill Core	0.126	14	5	0.29	94	<0.001	5	0.39	0.043	0.27	<0.1	1.29	3.1	0.4	1.09	<1	1.9
933062	Drill Core	0.112	16	3	0.44	71	0.002	4	0.51	0.045	0.26	<0.1	0.79	2.8	0.3	1.30	2	1.8
933063	Drill Core	0.126	22	3	0.60	107	0.004	3	0.62	0.058	0.23	0.1	0.46	3.3	0.2	0.81	3	0.5
933064	Drill Core	0.127	18	5	0.48	98	<0.001	4	0.51	0.057	0.31	<0.1	1.22	3.5	0.3	0.92	1	1.9
933065	Drill Core	0.121	16	4	0.54	53	<0.001	4	0.40	0.062	0.26	<0.1	1.21	3.0	0.2	1.62	1	1.9

QUALITY CONTROL REPORT

SMI08000932.1

Method	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
Unit	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	ppm	
MDL	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	0.1	2	0.01
Pulp Duplicates																					
933064	Drill Core	7.26	9.3	1889	8.1	35	0.6	3.0	8.4	517	2.97	40.6	3.8	121.5	11.2	741	0.2	3.7	0.1	23	2.39
REP 933064	QC		9.7	1897	7.7	37	0.5	2.7	8.5	514	2.99	40.0	3.8	118.2	11.0	727	0.1	3.5	0.1	24	2.39
Core Reject Duplicates																					
933034	Drill Core	7.80	2.0	1827	7.3	50	0.5	3.0	8.1	520	4.57	24.4	3.3	145.0	12.6	788	0.2	1.7	0.1	85	1.58
DUP 933034	QC		2.3	1606	11.1	38	0.7	2.5	7.9	633	3.12	13.1	5.6	84.8	14.9	371	0.2	5.9	0.1	38	2.59
Reference Materials																					
STD DS7	Standard		21.3	111.5	72.0	407	1.1	60.0	9.8	662	2.46	51.2	4.9	66.8	4.5	75	5.9	5.8	4.4	99	0.99
STD DS7	Standard		22.1	111.4	72.8	412	0.9	61.4	9.8	662	2.48	51.4	5.0	64.9	4.6	77	6.0	5.8	4.3	99	1.00
STD DS7	Standard		20.8	115.4	73.5	436	0.9	60.9	9.5	688	2.66	55.2	5.2	70.9	4.6	75	6.3	6.7	5.2	85	0.97
STD DS7	Standard		20.9	106.1	74.4	424	0.9	56.6	9.2	667	2.56	52.7	4.9	64.1	4.5	76	7.0	6.3	5.0	86	1.00
STD DS7	Standard		18.4	91.6	65.2	338	0.7	49.1	8.0	575	2.13	45.3	4.5	76.6	3.8	68	5.2	5.2	4.0	80	0.85
STD DS7	Standard		19.4	92.9	69.6	380	0.9	51.7	8.5	600	2.29	50.5	4.6	75.3	3.9	73	6.1	5.8	4.2	86	0.93
STD DS7	Standard		18.7	109.5	70.7	389	0.8	53.7	8.5	590	2.30	51.3	4.7	58.6	4.2	67	6.5	5.8	4.6	78	0.90
STD DS7	Standard		19.2	101.2	70.4	389	0.8	51.1	8.8	593	2.29	49.5	4.9	71.1	4.3	69	5.7	6.0	4.5	77	0.91
STD DS7 Expected			20.9	109	70.6	411	0.9	56	9.7	627	2.39	48.2	4.9	70	4.4	69	6.4	5.9	4.5	86	0.93
BLK	Blank		<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01
BLK	Blank		<0.1	0.9	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01
BLK	Blank		<0.1	3.0	<0.1	<1	<0.1	<0.1	<0.1	<1	0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01
BLK	Blank		<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01
Prep Wash																					
G1	Prep Blank	<0.01	0.4	2.2	3.1	45	<0.1	3.8	4.5	563	1.96	<0.5	2.0	2.5	3.8	62	<0.1	<0.1	<0.1	40	0.60
G1	Prep Blank	<0.01	0.3	2.3	3.9	50	<0.1	4.5	4.7	619	2.18	<0.5	2.2	1.0	4.2	64	<0.1	<0.1	<0.1	43	0.62

QUALITY CONTROL REPORT

SMI08000932.1

Method		1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte		P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
Unit		%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm
MDL		0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5
Pulp Duplicates																		
933064	Drill Core	0.127	18	5	0.48	98	<0.001	4	0.51	0.057	0.31	<0.1	1.22	3.5	0.3	0.92	1	1.9
REP 933064	QC	0.130	18	4	0.48	98	0.001	5	0.53	0.057	0.31	<0.1	1.25	3.4	0.4	0.93	1	1.6
Core Reject Duplicates																		
933034	Drill Core	0.137	21	6	0.57	242	0.025	2	0.53	0.027	0.14	0.1	0.20	3.5	<0.1	0.35	5	1.4
DUP 933034	QC	0.125	26	7	0.60	125	0.004	2	0.41	0.023	0.21	<0.1	0.25	3.5	0.1	0.65	2	1.2
Reference Materials																		
STD DS7	Standard	0.075	13	220	1.08	396	0.130	39	1.08	0.096	0.46	3.8	0.20	2.5	4.4	0.20	5	3.5
STD DS7	Standard	0.073	14	223	1.06	399	0.132	41	1.07	0.096	0.47	3.7	0.21	2.6	4.4	0.20	5	3.6
STD DS7	Standard	0.078	13	205	1.06	407	0.126	40	1.04	0.081	0.48	4.3	0.22	2.5	4.5	0.21	6	2.6
STD DS7	Standard	0.079	13	198	1.08	408	0.126	42	1.07	0.086	0.47	4.0	0.19	2.5	4.4	0.21	5	3.4
STD DS7	Standard	0.067	11	177	0.93	357	0.110	33	0.91	0.080	0.42	3.5	0.16	2.2	3.9	0.17	4	2.7
STD DS7	Standard	0.073	12	188	1.00	386	0.118	37	0.99	0.089	0.45	3.6	0.20	2.3	4.3	0.18	5	3.6
STD DS7	Standard	0.073	11	152	0.97	352	0.102	39	0.94	0.080	0.41	3.7	0.20	2.1	4.0	0.19	4	3.4
STD DS7	Standard	0.073	12	164	0.98	360	0.112	40	0.96	0.081	0.41	3.6	0.20	2.4	4.0	0.18	4	3.0
STD DS7 Expected		0.08	13	163	1.05	370	0.124	39	0.959	0.073	0.44	3.8	0.2	2.5	4.2	0.21	4.6	3.5
BLK	Blank	<0.001	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
BLK	Blank	<0.001	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
BLK	Blank	<0.001	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
BLK	Blank	<0.001	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
Prep Wash																		
G1	Prep Blank	0.079	7	11	0.61	231	0.129	<1	0.95	0.057	0.49	0.5	<0.01	2.1	0.3	<0.05	6	<0.5
G1	Prep Blank	0.087	8	13	0.65	246	0.141	<1	1.09	0.073	0.56	0.7	<0.01	2.7	0.4	<0.05	5	<0.5



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.

Vancouver BC V6C 1Z7 Canada

Submitted By:

Glen Garratt

Receiving Lab:

Canada-Smithers

Received:

September 19, 2008

Report Date:

October 15, 2008

Page:

1 of 2

CERTIFICATE OF ANALYSIS

SMI08000949.1

CLIENT JOB INFORMATION

Project: Zymo
Shipment ID: zy-rk-08-18
P.O. Number
Number of Samples: 10

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
DISP-RJT Dispose of Reject After 90 days

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Mincord Exploration Consultants Ltd.
110 - 325 Howe St.
Vancouver BC V6C 1Z7
Canada

CC: Bob Johnston

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status
R150	10	Crush, split and pulverize rock to 200 mesh		
1DX15	10	1:1:1 Aqua Regia digestion ICP-MS analysis	15	Completed

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only. All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.

** asterisk indicates that an analytical result could not be provided due to unusually high levels of interference from other elements.



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**

110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo

Report Date: October 15, 2008

Page: 2 of 2 Part 1

CERTIFICATE OF ANALYSIS

SMI08000949.1

Method	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
Unit	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	
MDL	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	
726807	Rock	2.06	10.1	780.8	67.5	187	1.9	2.3	9.7	879	2.82	33.6	0.5	64.3	3.0	11	1.9	0.9	1.1	21	0.76
726808	Rock	2.51	2.8	159.0	3.3	31	0.1	12.5	9.8	555	4.72	<0.5	0.3	6.9	1.0	140	<0.1	0.1	0.2	135	1.49
726809	Rock	2.60	3.9	1213	5.7	40	0.7	6.3	15.3	398	3.38	2.0	0.4	88.5	1.7	34	0.1	0.2	0.4	92	0.68
726810	Rock	1.43	51.6	529.3	11.3	64	0.3	5.8	12.6	321	3.56	10.5	6.1	46.5	12.7	43	0.3	0.9	0.4	15	0.22
726811	Rock	2.42	4.5	357.8	20.4	60	0.9	8.6	29.0	712	33.94	<0.5	0.2	70.3	0.6	9	0.3	<0.1	0.9	42	0.63
726812	Rock	1.78	0.7	65.0	5.2	18	<0.1	12.8	13.0	409	3.93	2.0	0.3	4.3	0.9	50	<0.1	1.1	<0.1	34	0.42
726813	Rock	2.33	1.5	21.2	2.3	7	<0.1	3.5	7.2	128	1.34	1.6	0.1	4.0	1.5	30	<0.1	0.3	0.1	8	0.13
726814	Rock	2.73	3.2	128.2	12.6	57	0.1	4.4	12.6	324	4.72	0.7	0.2	11.5	0.9	62	0.1	<0.1	0.2	64	0.20
726815	Rock	2.30	3.3	141.3	2.4	19	<0.1	6.8	7.6	258	3.86	1.2	0.2	16.3	1.3	14	<0.1	0.2	0.2	43	0.17
726816	Rock	2.86	21.6	761.4	6.6	25	0.5	4.7	10.7	180	4.75	1.5	0.7	142.8	3.9	97	<0.1	0.3	0.4	58	0.37



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.

Vancouver BC V6C 1Z7 Canada

Project:

Zymo

Report Date:

October 15, 2008

Page:

2 of 2

Part 2

CERTIFICATE OF ANALYSIS

SMI08000949.1

Method	Analyte	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
		P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
Unit		%	ppm	ppm	%	ppm	%	ppm	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
MDL		0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5
726807	Rock	0.079	14	2	0.26	78	<0.001	2	0.83	0.009	0.29	0.1	0.02	1.5	0.3	1.01	2	1.0
726808	Rock	0.068	3	33	1.11	183	0.275	<1	4.15	0.427	0.99	0.6	<0.01	16.4	1.1	1.03	12	<0.5
726809	Rock	0.081	7	11	1.02	59	0.150	1	1.50	0.096	0.20	0.7	<0.01	5.2	0.1	0.86	6	0.9
726810	Rock	0.153	51	2	0.03	101	0.001	3	0.59	0.038	0.24	0.1	<0.01	2.9	0.2	0.58	1	1.1
726811	Rock	0.225	8	6	0.39	6	0.004	5	2.77	0.002	0.01	<0.1	0.45	5.4	0.3	>10	7	12.0
726812	Rock	0.037	3	7	0.60	77	0.017	<1	2.79	0.120	0.19	<0.1	0.01	2.0	0.3	0.54	5	<0.5
726813	Rock	0.015	4	2	0.42	98	0.003	<1	1.09	0.053	0.20	<0.1	<0.01	0.9	0.2	0.33	2	<0.5
726814	Rock	0.052	3	14	0.47	50	0.057	1	1.20	0.064	0.16	0.1	0.04	6.7	0.2	1.43	5	1.2
726815	Rock	0.055	5	8	0.60	208	0.006	<1	1.51	0.031	0.40	<0.1	<0.01	2.3	0.5	0.32	4	<0.5
726816	Rock	0.128	7	8	1.02	59	0.053	<1	1.55	0.055	0.28	0.3	0.01	4.2	0.3	1.48	7	2.4

QUALITY CONTROL REPORT

SMI08000949.1

Method	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
Unit	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	
MDL	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	
Reference Materials																					
STD DS7	Standard	21.1	121.3	75.9	410	0.9	57.2	9.7	640	2.36	53.2	5.3	62.6	4.9	76	7.1	6.7	5.0	80	0.98	
STD DS7	Standard	21.3	113.0	76.1	404	0.8	55.9	9.3	626	2.33	53.8	5.4	68.1	5.1	76	7.3	6.5	4.9	80	0.99	
STD DS7	Standard	20.1	114.7	74.4	410	0.8	54.8	9.7	606	2.34	57.0	5.4	60.6	5.1	79	7.5	7.1	4.9	71	0.97	
STD DS7	Standard	19.9	123.0	76.8	445	0.9	57.8	9.9	644	2.38	59.9	5.6	67.0	5.0	83	7.5	6.9	5.0	75	0.97	
STD DS7 Expected		20.9	109	70.6	411	0.9	56	9.7	627	2.39	48.2	4.9	70	4.4	69	6.4	5.9	4.5	86	0.93	
BLK	Blank	<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01	
BLK	Blank	<0.1	0.6	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	3.6	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01	
Prep Wash																					
G1	Prep Blank	<0.01	0.6	11.6	2.7	52	<0.1	4.4	4.9	627	2.25	<0.5	2.1	0.8	4.8	69	<0.1	<0.1	0.1	42	0.57
G1	Prep Blank	<0.01	0.4	7.5	2.8	52	<0.1	4.5	5.3	637	2.23	<0.5	2.1	<0.5	4.6	69	<0.1	<0.1	0.1	43	0.57

QUALITY CONTROL REPORT

SMI08000949.1

Method		1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte		P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
Unit		%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm
MDL		0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5
Reference Materials																		
STD DS7	Standard	0.080	14	196	1.08	397	0.128	42	1.09	0.091	0.46	3.9	0.22	2.6	4.3	0.20	5	3.7
STD DS7	Standard	0.079	14	190	1.07	408	0.127	38	1.07	0.091	0.45	3.9	0.21	2.6	4.2	0.20	5	3.2
STD DS7	Standard	0.085	14	166	0.97	379	0.121	39	0.97	0.084	0.44	4.2	0.19	2.7	4.1	0.18	5	3.8
STD DS7	Standard	0.085	14	177	1.02	381	0.122	37	1.00	0.083	0.48	4.1	0.21	2.7	4.4	0.18	5	3.6
STD DS7 Expected		0.08	13	163	1.05	370	0.124	39	0.959	0.073	0.44	3.8	0.2	2.5	4.2	0.21	4.6	3.5
BLK	Blank	<0.001	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
BLK	Blank	<0.001	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
Prep Wash																		
G1	Prep Blank	0.092	10	13	0.66	289	0.148	<1	1.08	0.079	0.60	1.6	<0.01	2.4	0.4	<0.05	6	<0.5
G1	Prep Blank	0.089	10	14	0.66	290	0.154	<1	1.12	0.077	0.60	<0.1	<0.01	2.5	0.4	<0.05	6	<0.5

CERTIFICATE OF ANALYSIS

SMI08000950.1

CLIENT JOB INFORMATION

Project: Zymo
 Shipment ID: zy-co-08-03
 P.O. Number
 Number of Samples: 52

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
 DISP-RJT Dispose of Reject After 90 days

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7
 Canada

CC: Bob Johnston

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status
R150	51	Crush split and pulverize drill core to 200 mesh		
1DX15	52	1:1:1 Aqua Regia digestion ICP-MS analysis	15	Completed

ADDITIONAL COMMENTS





AcmeLabs ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
Report Date: October 16, 2008

Page: 2 of 3 **Part** 1

CERTIFICATE OF ANALYSIS

SMI08000950.1

Method	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
Unit	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	
MDL	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	
933066	Drill Core	8.36	4.9	1557	10.0	34	0.6	3.1	7.5	577	2.82	23.6	4.6	96.6	12.3	433	0.2	2.4	0.2	16	2.69
933067	Drill Core	8.01	9.4	1620	11.9	34	0.6	3.2	7.9	568	2.55	20.2	5.0	105.5	13.9	614	0.2	1.2	0.2	25	2.88
933068	Drill Core	8.14	10.3	1519	9.8	38	0.5	3.1	7.8	503	2.74	7.5	4.9	100.0	13.8	1073	0.2	1.8	0.2	41	2.81
933069	Drill Core	8.21	20.0	2649	8.2	56	0.8	4.2	14.8	491	3.42	23.1	2.4	157.4	6.4	673	0.2	19.1	0.2	52	3.00
933070	Drill Core	7.62	42.7	1963	15.3	38	0.8	4.2	9.4	572	2.05	39.4	1.4	129.0	2.1	227	0.2	15.3	0.2	16	2.89
933071	Drill Core	7.64	44.2	1377	21.0	41	0.6	3.1	7.9	637	2.44	22.4	3.8	58.1	7.0	374	0.2	4.6	0.2	10	4.45
933072	Drill Core	7.89	12.0	2279	13.1	34	0.8	3.3	8.9	657	2.79	20.4	5.5	122.3	10.7	657	0.2	6.2	0.2	14	4.28
933073	Drill Core	8.49	7.7	2854	9.5	41	0.8	4.1	10.9	439	2.54	24.5	3.4	178.1	10.3	1024	0.3	14.3	0.2	23	3.30
933074	Drill Core	8.09	50.3	1056	13.4	33	0.4	4.0	8.6	364	1.38	29.3	2.8	71.2	2.2	393	0.1	1.3	0.2	20	2.02
933075	Drill Core	7.02	102.0	1299	22.9	45	0.4	3.3	5.2	428	1.12	9.3	2.3	74.3	1.8	413	0.3	2.0	0.2	11	2.49
933076	Drill Core	6.60	67.9	639.2	16.0	29	0.2	3.2	5.9	409	1.12	3.6	1.1	57.8	2.0	382	0.2	0.7	0.1	17	2.09
933077	Drill Core	7.69	81.0	1106	15.5	26	0.3	3.0	6.0	346	1.15	3.3	1.1	77.8	3.1	340	0.2	0.9	0.2	14	2.27
933078	Drill Core	7.39	52.6	4001	13.1	53	1.3	5.5	21.4	393	3.29	12.9	1.5	235.0	4.0	382	0.3	1.0	0.2	29	2.87
933079	Drill Core	7.32	96.8	2080	19.8	52	0.8	5.7	13.1	660	2.65	87.4	1.6	110.2	2.0	321	0.4	2.9	0.3	20	2.45
933080	Drill Core	6.97	105.7	1183	10.7	44	0.4	7.9	9.9	544	2.39	2.0	1.1	95.2	2.3	189	0.1	0.2	0.2	59	1.68
933081	Drill Core	6.67	60.8	649.0	8.8	32	0.3	7.1	9.3	571	2.28	11.7	0.9	74.2	2.0	167	0.2	0.4	0.2	58	2.66
933082	Drill Core	6.94	75.1	504.1	6.2	26	0.2	6.3	7.7	525	2.01	2.5	0.9	46.3	2.1	402	0.1	0.2	0.1	29	1.59
933083	Drill Core	6.71	130.2	778.6	13.8	72	0.3	6.3	9.3	599	1.96	6.2	0.7	80.7	1.9	664	1.0	0.3	0.2	24	2.39
933084	Drill Core	6.89	170.9	573.7	25.6	34	0.2	5.0	6.6	850	1.57	38.5	0.4	47.4	2.0	434	0.4	0.2	0.1	15	4.90
933085	Drill Core	6.79	86.8	1091	24.5	34	0.4	5.7	10.3	608	1.55	168.3	0.5	81.9	1.8	171	0.4	0.3	0.2	17	2.30
933086	Drill Core	5.47	66.3	499.6	49.7	150	0.4	6.0	12.3	448	1.49	26.2	0.4	43.3	1.1	87	1.6	0.3	0.2	15	1.23
933088	Drill Core	4.81	28.8	3431	6.9	32	1.5	3.6	10.2	429	4.72	7.6	3.9	199.2	12.1	471	0.2	1.9	0.3	46	1.31
933089	Drill Core	7.08	5.3	2153	6.9	32	0.9	2.8	8.0	360	4.48	3.7	3.6	156.5	15.7	364	0.1	6.0	0.2	49	1.42
933090	Rock Pulp	0.04	8.5	2982	14.4	131	0.5	145.2	14.7	771	5.63	13.9	0.2	231.9	1.4	189	0.7	8.2	0.4	52	2.63
933091	Drill Core	7.48	2.3	580.9	23.7	29	0.3	2.3	5.9	437	2.47	6.4	7.9	51.5	18.2	595	0.2	13.4	0.1	32	2.34
933092	Drill Core	7.06	9.0	745.6	8.4	32	0.3	1.9	6.1	446	3.10	8.9	4.3	51.5	17.8	488	0.1	14.9	0.1	33	2.12
933093	Drill Core	7.32	6.3	1772	9.7	29	0.7	2.7	9.4	357	2.83	81.2	4.7	100.0	17.0	158	0.1	75.3	0.2	11	2.02
933094	Drill Core	6.43	14.3	1109	7.4	23	0.5	2.2	6.2	333	2.59	12.6	6.4	61.4	19.7	1056	0.1	5.0	0.2	30	2.38
933095	Drill Core	7.10	2.4	1549	6.6	27	0.6	3.0	8.0	324	2.80	7.4	6.4	96.1	20.2	1689	0.1	1.9	0.1	47	1.82
933096	Drill Core	6.65	25.6	839.5	8.2	26	0.3	2.1	6.2	435	2.37	10.9	10.2	39.5	20.0	539	<0.1	8.0	0.1	28	2.41

This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
 Report Date: October 16, 2008

Page: 2 of 3 Part 2

CERTIFICATE OF ANALYSIS

SMI08000950.1

Method	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se	
Unit	%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
MDL	0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5	
933066	Drill Core	0.128	17	6	0.52	140	0.001	4	0.55	0.057	0.32	1.6	0.50	3.6	0.2	0.81	1	1.1
933067	Drill Core	0.133	24	4	0.60	227	0.003	3	0.63	0.052	0.27	0.4	0.37	3.4	0.3	0.50	3	1.3
933068	Drill Core	0.129	28	5	0.66	222	0.003	2	0.79	0.063	0.19	0.2	0.25	3.6	0.1	0.58	4	1.1
933069	Drill Core	0.159	20	5	1.08	168	0.025	2	1.24	0.083	0.36	0.1	0.28	5.8	0.3	0.75	5	1.7
933070	Drill Core	0.079	7	2	0.61	112	0.002	3	0.76	0.074	0.41	<0.1	1.09	4.6	0.3	0.95	2	1.4
933071	Drill Core	0.093	10	2	0.55	57	<0.001	3	0.55	0.065	0.29	<0.1	0.85	3.5	0.2	1.39	1	1.2
933072	Drill Core	0.124	17	3	0.69	62	<0.001	5	0.58	0.050	0.28	<0.1	0.70	3.1	0.2	1.35	2	2.0
933073	Drill Core	0.152	20	3	0.64	118	0.003	3	0.71	0.069	0.32	<0.1	0.49	4.0	0.2	1.00	2	1.8
933074	Drill Core	0.064	11	3	0.38	212	0.005	2	0.83	0.080	0.45	<0.1	0.26	3.9	0.3	0.59	3	<0.5
933075	Drill Core	0.043	9	2	0.31	313	0.001	2	0.65	0.080	0.36	<0.1	0.33	4.2	0.3	0.46	2	0.7
933076	Drill Core	0.037	12	3	0.31	540	0.001	2	0.88	0.070	0.44	<0.1	0.20	3.6	0.3	0.24	3	<0.5
933077	Drill Core	0.071	15	2	0.33	344	0.001	2	0.83	0.071	0.43	<0.1	0.24	3.1	0.3	0.36	2	0.7
933078	Drill Core	0.148	17	3	0.69	75	0.006	2	1.09	0.067	0.32	0.1	0.43	2.9	0.2	1.50	4	3.0
933079	Drill Core	0.116	9	3	0.45	50	0.002	3	0.87	0.069	0.42	0.2	1.16	4.2	0.4	1.72	3	1.9
933080	Drill Core	0.066	14	7	0.49	347	0.004	2	1.26	0.079	0.41	<0.1	0.13	5.0	0.3	0.32	5	0.6
933081	Drill Core	0.485	18	6	0.53	308	0.005	2	1.51	0.073	0.57	<0.1	0.08	5.0	0.4	0.23	5	<0.5
933082	Drill Core	0.054	10	3	0.44	331	0.002	2	1.06	0.078	0.48	<0.1	0.09	3.8	0.4	0.24	3	<0.5
933083	Drill Core	0.053	10	3	0.54	395	0.002	3	1.20	0.074	0.55	<0.1	0.25	4.3	0.4	0.34	3	<0.5
933084	Drill Core	0.036	11	2	0.47	539	<0.001	2	0.86	0.070	0.42	<0.1	0.14	3.7	0.3	0.25	2	0.6
933085	Drill Core	0.047	8	3	0.37	299	0.002	3	0.97	0.070	0.56	<0.1	0.17	3.4	0.4	0.51	2	1.1
933086	Drill Core	0.021	7	2	0.30	225	0.002	2	1.11	0.065	0.64	<0.1	0.61	3.5	0.4	0.41	3	0.7
933088	Drill Core	0.096	19	6	0.52	211	0.002	3	0.52	0.023	0.26	<0.1	0.30	3.4	0.2	0.62	3	2.2
933089	Drill Core	0.094	23	7	0.46	331	0.005	2	0.50	0.035	0.20	<0.1	0.20	3.6	<0.1	0.33	4	1.1
933090	Rock Pulp	0.109	6	196	1.07	71	0.002	7	1.15	0.047	0.42	0.5	1.21	6.6	0.2	2.76	3	8.2
933091	Drill Core	0.106	28	6	0.50	389	0.007	4	0.46	0.036	0.25	<0.1	0.16	3.5	0.1	0.23	2	0.8
933092	Drill Core	0.113	26	4	0.52	541	0.002	4	0.44	0.024	0.28	<0.1	0.24	3.8	0.1	0.23	2	0.7
933093	Drill Core	0.127	9	5	0.43	104	<0.001	<1	0.46	0.005	0.36	<0.1	0.38	3.0	0.3	0.58	1	1.6
933094	Drill Core	0.136	22	4	0.56	270	0.002	<1	0.45	0.024	0.29	<0.1	0.20	3.3	0.2	0.43	2	0.9
933095	Drill Core	0.141	25	7	0.62	305	0.011	<1	0.62	0.033	0.29	<0.1	0.22	3.6	0.2	0.44	3	1.4
933096	Drill Core	0.135	23	4	0.54	344	0.002	<1	0.46	0.017	0.28	<0.1	0.13	3.3	0.2	0.36	2	0.8



AcmeLabs ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
Report Date: October 16, 2008

Page: 3 of 3 **Part** 1

CERTIFICATE OF ANALYSIS

SMI08000950.1

Method	Analyte	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca
Unit		kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%
MDL		0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	0.1	2	0.01
933097	Drill Core	6.53	4.1	1346	8.2	28	0.5	3.1	7.2	369	2.80	7.0	6.0	88.4	21.0	1087	<0.1	3.6	0.1	42	2.02
933098	Drill Core	6.92	2.2	880.6	5.7	27	0.3	2.5	6.9	297	2.60	4.0	5.4	57.9	20.3	579	0.1	5.8	<0.1	38	2.37
933099	Drill Core	7.40	4.2	1061	14.6	32	0.4	2.5	7.5	1113	3.04	80.7	7.3	64.8	17.8	245	0.1	4.2	0.1	17	4.95
933100	Drill Core	6.62	1.8	1514	10.3	26	0.5	2.8	8.4	564	2.65	15.0	7.4	86.1	22.0	517	0.1	5.1	0.2	27	2.40
933101	Drill Core	7.10	4.3	1119	13.1	42	0.4	2.7	7.2	956	2.60	16.5	7.7	46.0	19.8	298	0.2	2.5	0.1	27	3.09
933102	Drill Core	8.10	6.8	895.0	26.7	54	0.5	2.7	7.5	2148	3.25	93.1	5.9	53.1	17.0	176	0.3	3.1	0.1	16	3.59
933103	Drill Core	6.25	5.8	565.8	9.6	30	0.2	2.4	6.8	853	2.69	72.4	5.5	26.6	19.6	198	0.1	3.5	0.1	19	3.08
933104	Drill Core	6.68	64.2	962.9	14.5	30	0.5	2.9	7.7	1366	3.04	97.4	6.6	45.7	17.0	191	0.2	19.8	0.2	20	3.66
933105	Drill Core	6.64	12.0	5307	22.3	60	2.5	5.4	14.0	1643	7.49	45.7	2.3	336.1	5.0	105	0.3	5.3	0.7	46	2.01
933106	Drill Core	8.13	16.0	4501	9.2	64	1.9	5.7	15.1	585	9.91	11.1	3.1	299.8	8.2	131	0.1	3.1	0.3	92	1.48
933107	Drill Core	6.80	20.7	3015	6.9	37	1.1	3.8	10.5	372	5.08	5.4	3.1	237.4	14.7	1153	0.2	2.7	0.2	58	1.80
933108	Drill Core	7.74	4.7	3009	8.5	50	1.1	4.6	12.5	449	6.22	3.8	3.0	177.8	15.1	404	0.2	1.3	0.3	73	1.18
933109	Drill Core	7.84	2.8	4135	5.9	67	1.2	5.7	14.3	497	6.96	2.2	1.4	268.8	8.1	482	0.2	0.4	0.3	89	1.14
933110	Drill Core	7.06	1.9	4135	7.5	82	1.1	7.0	18.5	685	9.70	2.9	2.0	293.9	12.6	223	0.3	0.9	0.3	124	1.85
933111	Drill Core	6.71	2.9	4457	8.1	78	1.2	4.9	12.7	476	5.82	4.7	0.4	326.0	2.6	151	0.3	2.9	0.3	55	1.27
933112	Drill Core	7.92	4.2	4878	12.0	63	1.6	4.4	11.7	378	4.95	1.7	0.6	371.3	3.6	77	0.2	0.7	0.3	57	0.91
933113	Drill Core	6.99	7.4	5789	4.3	62	1.5	4.8	13.3	350	4.37	0.6	2.5	433.1	11.5	932	0.3	0.5	0.3	66	1.23
933114	Drill Core	6.86	24.1	1225	7.1	32	0.6	3.1	8.9	502	3.32	13.4	5.6	91.1	20.3	269	0.1	9.0	0.1	33	2.42
933115	Drill Core	7.00	11.5	2725	5.6	39	1.0	3.7	11.4	344	4.28	1.8	3.1	149.0	14.3	1260	0.1	0.6	0.2	59	1.68
933116	Drill Core	7.39	10.0	2234	5.5	30	1.1	3.7	8.5	293	3.37	2.9	6.8	119.2	19.9	1270	0.1	1.7	0.2	52	1.91
933117	Drill Core	4.24	3.6	1760	11.7	36	0.6	3.7	8.5	311	3.43	20.6	3.2	109.9	14.6	1176	0.1	1.4	0.1	41	1.70
933118	Drill Core	6.71	5.1	3072	20.6	77	1.0	4.3	8.5	909	3.96	10.5	0.4	160.8	1.9	104	0.3	2.7	0.2	34	3.54



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.

Vancouver BC V6C 1Z7 Canada

Project:

Zymo

Report Date:

October 16, 2008

Page:

3 of 3

Part 2

CERTIFICATE OF ANALYSIS

SMI08000950.1

Method	Analyte	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
		P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
Unit		%	ppm	ppm	%	ppm	%	ppm	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
MDL		0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.05	1	1	0.5
933097	Drill Core	0.138	27	6	0.58	282	0.005	<1	0.53	0.032	0.27	<0.1	0.16	3.3	0.1	0.48	3	1.2
933098	Drill Core	0.145	27	4	0.61	418	0.004	<1	0.55	0.027	0.28	<0.1	0.10	3.2	0.1	0.30	3	0.8
933099	Drill Core	0.139	20	3	1.31	161	<0.001	<1	0.47	0.009	0.30	<0.1	0.34	3.2	0.2	0.99	1	1.8
933100	Drill Core	0.143	21	4	0.56	217	0.001	<1	0.53	0.018	0.34	<0.1	0.30	3.2	0.2	0.64	2	1.5
933101	Drill Core	0.139	22	4	0.71	69	<0.001	<1	0.53	0.014	0.33	<0.1	0.38	3.5	0.3	1.02	1	1.1
933102	Drill Core	0.133	15	3	0.98	60	<0.001	<1	0.44	0.007	0.28	<0.1	0.79	2.7	0.3	2.22	1	2.5
933103	Drill Core	0.141	12	3	0.65	228	<0.001	<1	0.47	0.007	0.31	<0.1	0.93	3.5	0.3	0.63	1	0.8
933104	Drill Core	0.134	13	3	1.00	85	<0.001	<1	0.44	0.005	0.30	<0.1	0.74	3.2	0.3	1.46	1	1.9
933105	Drill Core	0.049	4	11	0.83	28	<0.001	<1	0.33	0.007	0.27	<0.1	0.92	2.7	0.4	2.16	2	4.6
933106	Drill Core	0.075	6	8	0.61	140	0.002	<1	0.41	0.015	0.31	<0.1	0.32	3.8	0.2	0.83	4	2.8
933107	Drill Core	0.138	15	6	0.71	242	0.008	<1	0.53	0.023	0.30	<0.1	0.13	4.4	0.2	0.55	4	1.8
933108	Drill Core	0.124	13	5	0.66	239	0.014	<1	0.58	0.033	0.21	<0.1	0.27	3.6	0.1	0.50	6	2.1
933109	Drill Core	0.131	10	6	1.05	145	0.051	<1	0.86	0.044	0.34	<0.1	0.34	5.7	0.3	0.60	8	2.9
933110	Drill Core	0.202	16	7	1.12	126	0.033	<1	0.94	0.043	0.31	<0.1	0.38	7.5	0.2	0.66	10	3.2
933111	Drill Core	0.052	4	7	0.73	128	0.020	<1	0.66	0.043	0.35	<0.1	0.30	4.9	0.2	0.57	4	3.0
933112	Drill Core	0.071	6	8	0.60	138	0.013	<1	0.69	0.041	0.25	<0.1	0.22	3.3	0.1	0.67	5	3.3
933113	Drill Core	0.162	18	5	0.84	174	0.033	<1	0.92	0.045	0.19	0.1	0.34	3.4	<0.1	0.75	7	4.8
933114	Drill Core	0.157	23	5	0.73	135	0.002	<1	0.53	0.034	0.32	<0.1	0.32	4.5	0.2	0.78	2	1.2
933115	Drill Core	0.175	17	5	0.82	266	0.022	<1	0.59	0.038	0.29	<0.1	0.14	4.0	0.1	0.62	4	2.3
933116	Drill Core	0.170	22	6	0.79	178	0.017	<1	0.67	0.043	0.30	<0.1	0.14	4.3	0.1	0.60	4	1.7
933117	Drill Core	0.151	17	4	0.66	244	0.010	<1	0.63	0.041	0.37	<0.1	0.23	5.3	0.2	0.53	3	1.5
933118	Drill Core	0.044	3	3	0.96	271	<0.001	<1	0.40	0.034	0.31	<0.1	0.28	5.2	0.2	0.50	1	2.0

QUALITY CONTROL REPORT

SMI08000950.1

Method	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
Unit	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	
MDL	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	
Pulp Duplicates																					
933072	Drill Core	7.89	12.0	2279	13.1	34	0.8	3.3	8.9	657	2.79	20.4	5.5	122.3	10.7	657	0.2	6.2	0.2	14	4.28
REP 933072	QC		11.7	2246	12.8	33	0.8	3.3	8.9	665	2.79	20.5	5.8	104.3	10.8	650	0.2	6.2	0.2	13	4.24
Core Reject Duplicates																					
933070	Drill Core	7.62	42.7	1963	15.3	38	0.8	4.2	9.4	572	2.05	39.4	1.4	129.0	2.1	227	0.2	15.3	0.2	16	2.89
DUP 933070	QC		47.0	1939	15.9	37	0.7	4.2	10.1	608	2.14	36.4	1.4	90.0	2.3	230	0.2	16.1	0.2	17	2.99
933106	Drill Core	8.13	16.0	4501	9.2	64	1.9	5.7	15.1	585	9.91	11.1	3.1	299.8	8.2	131	0.1	3.1	0.3	92	1.48
DUP 933106	QC		9.4	4451	8.1	57	1.8	4.9	14.5	569	9.16	9.9	3.0	285.0	7.7	122	0.1	3.1	0.3	86	1.45
Reference Materials																					
STD DS7	Standard		20.1	114.7	74.4	410	0.8	54.8	9.7	606	2.34	57.0	5.4	60.6	5.1	79	7.5	7.1	4.9	71	0.97
STD DS7	Standard		19.9	123.0	76.8	445	0.9	57.8	9.9	644	2.38	59.9	5.6	67.0	5.0	83	7.5	6.9	5.0	75	0.97
STD DS7	Standard		20.1	118.3	77.1	437	0.9	55.5	9.9	616	2.40	59.0	5.5	99.6	5.2	80	7.6	6.5	5.3	82	0.99
STD DS7	Standard		21.3	118.8	79.4	431	0.9	56.3	9.8	657	2.44	60.4	5.8	78.9	5.3	83	7.7	6.8	5.6	82	1.01
STD DS7 Expected			20.9	109	70.6	411	0.9	56	9.7	627	2.39	48.2	4.9	70	4.4	69	6.4	5.9	4.5	86	0.93
BLK	Blank		<0.1	0.6	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	3.6	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01
BLK	Blank		<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01
Prep Wash																					
G1	Prep Blank	<0.01	0.6	2.4	2.3	49	<0.1	5.1	4.6	543	2.04	<0.5	1.9	1.5	4.4	67	<0.1	<0.1	0.4	36	0.59
G1	Prep Blank	<0.01	0.5	2.2	2.6	51	<0.1	4.9	4.8	575	2.04	<0.5	1.8	<0.5	4.7	73	<0.1	<0.1	0.1	36	0.75

QUALITY CONTROL REPORT

SMI08000950.1

Method		1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
Analyte		P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
Unit		%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm
MDL		0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5
Pulp Duplicates																		
933072	Drill Core	0.124	17	3	0.69	62	<0.001	5	0.58	0.050	0.28	<0.1	0.70	3.1	0.2	1.35	2	2.0
REP 933072	QC	0.127	17	3	0.70	65	<0.001	4	0.56	0.049	0.26	<0.1	0.66	3.0	0.2	1.36	1	1.5
Core Reject Duplicates																		
933070	Drill Core	0.079	7	2	0.61	112	0.002	3	0.76	0.074	0.41	<0.1	1.09	4.6	0.3	0.95	2	1.4
DUP 933070	QC	0.086	8	2	0.63	146	0.003	3	0.84	0.079	0.48	<0.1	0.93	4.7	0.4	0.97	2	1.6
933106	Drill Core	0.075	6	8	0.61	140	0.002	<1	0.41	0.015	0.31	<0.1	0.32	3.8	0.2	0.83	4	2.8
DUP 933106	QC	0.065	6	7	0.59	154	0.001	<1	0.32	0.012	0.27	<0.1	0.27	3.4	0.2	0.78	3	2.7
Reference Materials																		
STD DS7	Standard	0.085	14	166	0.97	379	0.121	39	0.97	0.084	0.44	4.2	0.19	2.7	4.1	0.18	5	3.8
STD DS7	Standard	0.085	14	177	1.02	381	0.122	37	1.00	0.083	0.48	4.1	0.21	2.7	4.4	0.18	5	3.6
STD DS7	Standard	0.091	13	169	1.07	372	0.123	31	1.05	0.087	0.44	4.1	0.21	2.5	4.2	0.19	5	3.6
STD DS7	Standard	0.088	14	174	1.05	401	0.129	34	1.02	0.087	0.48	4.1	0.20	2.7	4.4	0.19	5	4.0
STD DS7 Expected		0.08	13	163	1.05	370	0.124	39	0.959	0.073	0.44	3.8	0.2	2.5	4.2	0.21	4.6	3.5
BLK	Blank	<0.001	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
BLK	Blank	<0.001	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
Prep Wash																		
G1	Prep Blank	0.090	9	14	0.56	265	0.135	<1	0.98	0.076	0.56	0.1	<0.01	2.3	0.4	<0.05	5	<0.5
G1	Prep Blank	0.089	8	13	0.60	281	0.137	<1	1.03	0.086	0.60	<0.1	<0.01	2.5	0.4	<0.05	5	<0.5



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.

Vancouver BC V6C 1Z7 Canada

Submitted By:

Glen Garratt

Receiving Lab:

Canada-Smithers

Received:

September 23, 2008

Report Date:

October 17, 2008

Page:

1 of 3

CERTIFICATE OF ANALYSIS

SMI08000963.1

CLIENT JOB INFORMATION

Project: Zymo
Shipment ID: zy-co-08-04
P.O. Number
Number of Samples: 50

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
DISP-RJT Dispose of Reject After 90 days

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Mincord Exploration Consultants Ltd.
110 - 325 Howe St.
Vancouver BC V6C 1Z7
Canada

CC: Bob Johnston

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status
R150	48	Crush split and pulverize drill core to 200 mesh		
1DX15	50	1:1:1 Aqua Regia digestion ICP-MS analysis	15	Completed

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only. All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.

“**” asterisk indicates that an analytical result could not be provided due to unusually high levels of interference from other elements.



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**

110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo

Report Date: October 17, 2008

Page: 2 of 3 Part 1

CERTIFICATE OF ANALYSIS

SMI08000963.1

Method	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
Unit	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	
MDL	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	
933119	Drill Core	6.95	3.5	1366	11.2	39	0.5	2.4	7.1	487	2.90	17.9	3.6	68.5	14.3	645	0.1	4.9	0.1	25	2.11
933120	Rock Pulp	0.04	7.8	3029	15.9	131	0.5	128.0	14.5	783	5.46	12.5	0.2	207.3	1.5	168	0.5	10.1	0.5	50	2.71
933121	Drill Core	7.40	4.8	6975	8.9	66	1.7	5.3	13.8	568	4.83	1.2	1.0	418.5	4.0	74	0.3	1.1	0.4	76	1.43
933122	Drill Core	6.34	7.4	9588	12.5	79	2.3	6.5	16.2	465	5.21	12.6	1.0	669.7	2.0	196	0.3	1.7	0.4	65	1.33
933123	Drill Core	4.38	31.3	4504	16.1	60	1.5	3.7	10.7	437	3.06	18.9	0.4	245.6	1.6	85	0.2	5.5	0.3	23	1.51
933124	Drill Core	5.18	31.0	3801	10.3	66	1.2	9.2	12.5	515	3.00	235.6	2.5	218.5	5.0	60	0.2	79.8	0.3	26	2.01
933125	Drill Core	4.82	50.8	3167	13.1	60	1.4	9.1	12.9	531	3.26	279.4	2.9	177.5	7.5	66	0.2	104.5	0.3	19	2.20
933126	Drill Core	6.07	95.7	1248	15.2	26	0.5	4.7	7.6	308	1.53	72.0	1.8	67.2	2.0	52	0.1	18.5	0.2	10	1.05
933127	Drill Core	5.76	39.1	933.6	26.7	55	0.4	3.8	7.2	145	0.69	144.0	0.4	33.6	0.9	27	0.4	25.1	0.1	5	0.41
933128	Drill Core	5.68	61.6	710.4	11.1	11	0.3	4.5	4.1	62	0.31	69.6	0.7	40.0	1.6	23	<0.1	16.6	0.1	5	0.23
933129	Drill Core	6.50	88.0	1047	13.2	13	0.3	5.0	9.4	295	1.15	166.2	0.4	54.2	0.8	44	<0.1	8.5	0.2	8	0.80
933130	Drill Core	6.93	43.4	780.7	27.6	29	0.5	4.2	9.5	560	1.85	229.4	0.4	45.4	0.6	44	0.1	24.8	0.2	9	1.28
933131	Drill Core	8.16	59.0	1197	12.4	36	0.9	4.5	14.0	825	3.03	19.5	0.7	110.9	2.1	286	0.2	10.0	0.2	25	2.66
933132	Drill Core	5.57	42.7	670.1	14.8	35	0.3	7.1	10.9	615	2.51	3.7	2.3	45.6	1.3	193	0.2	0.6	0.2	29	1.32
933133	Drill Core	3.42	35.5	810.7	8.6	20	0.3	3.9	9.2	526	2.49	1.0	0.3	47.0	1.2	203	<0.1	0.2	0.2	14	1.00
933134	Drill Core	9.41	18.5	1884	5.7	55	0.6	6.7	28.1	388	5.22	5.6	0.9	95.5	4.2	438	0.2	0.4	0.2	94	2.36
933135	Drill Core	7.92	39.5	1294	14.2	37	0.7	6.9	14.0	584	3.58	5.3	0.3	65.3	0.7	64	0.2	3.1	0.3	34	1.30
933136	Drill Core	7.02	38.6	880.0	9.1	33	0.4	7.1	14.9	440	2.54	15.3	0.2	38.3	0.8	30	0.2	21.4	0.2	22	0.77
933137	Drill Core	8.21	52.3	839.9	5.6	32	0.4	5.9	16.0	588	3.39	8.7	0.4	37.1	1.0	32	0.1	16.0	0.2	26	0.87
933138	Drill Core	7.22	32.3	1563	8.9	41	0.5	7.1	20.5	755	4.50	3.7	0.3	80.0	0.7	42	0.2	2.5	0.2	37	1.41
933139	Drill Core	7.38	42.5	746.2	9.0	32	0.3	6.6	14.5	649	3.13	3.8	0.3	34.1	1.0	35	0.1	5.4	0.2	33	0.92
933140	Drill Core	8.08	26.1	1496	13.2	41	0.5	6.3	18.5	604	3.82	2.1	0.5	83.3	1.0	56	0.2	2.0	0.2	51	1.45
933141	Drill Core	7.52	44.9	1783	10.4	46	0.7	4.9	15.3	387	3.42	15.2	1.4	102.5	3.7	458	0.2	25.4	0.2	43	2.27
933142	Drill Core	7.12	24.9	1463	12.3	51	0.5	3.5	15.2	301	3.63	7.2	3.4	93.8	10.1	281	0.3	75.1	0.2	49	1.93
933143	Drill Core	7.70	45.7	2148	11.5	46	0.7	3.6	16.8	293	3.78	11.2	3.1	140.9	9.8	392	0.3	5.5	0.2	45	2.61
933144	Drill Core	8.22	26.1	2167	11.9	46	0.7	3.9	16.4	296	3.13	68.4	3.4	135.3	9.1	689	0.3	3.5	0.2	31	2.19
933145	Drill Core	6.73	29.3	1366	10.1	42	0.4	2.8	14.5	326	2.72	63.2	3.4	90.0	9.3	119	0.3	20.2	0.2	15	2.85
933146	Drill Core	7.82	12.2	853.9	8.1	45	0.3	3.3	14.3	321	3.61	4.2	3.9	37.5	9.5	1129	0.2	2.4	0.2	34	2.83
933147	Drill Core	7.53	25.5	1436	11.3	47	0.5	3.1	16.8	320	3.59	7.5	4.3	69.4	10.0	1977	0.3	1.8	0.3	33	3.03
933148	Drill Core	7.79	16.8	1178	12.8	50	0.4	3.1	16.9	381	3.88	7.0	4.4	52.3	9.8	629	0.3	2.1	0.2	30	3.34



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
 Report Date: October 17, 2008

Page: 2 of 3 Part 2

CERTIFICATE OF ANALYSIS

SMI08000963.1

Method	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se	
Unit	%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
MDL	0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5	
933119	Drill Core	0.112	20	7	0.60	357	0.002	6	0.55	0.042	0.31	0.2	0.21	3.9	<0.1	0.38	2	1.1
933120	Rock Pulp	0.110	6	183	1.11	40	0.002	5	1.04	0.055	0.34	0.5	1.22	6.3	0.1	2.82	3	8.9
933121	Drill Core	0.078	7	14	0.48	138	0.009	2	0.66	0.049	0.25	0.2	0.29	4.4	<0.1	0.89	5	4.7
933122	Drill Core	0.052	5	10	0.45	76	0.008	3	0.57	0.050	0.27	<0.1	0.45	4.9	0.1	1.32	4	6.5
933123	Drill Core	0.012	3	4	0.27	152	<0.001	3	0.29	0.042	0.24	<0.1	0.22	3.0	0.1	0.77	1	2.3
933124	Drill Core	0.116	8	6	0.50	135	0.001	6	0.54	0.044	0.30	0.2	0.30	4.2	0.4	0.90	1	3.1
933125	Drill Core	0.112	8	7	0.52	91	0.001	7	0.39	0.035	0.24	0.1	0.60	3.7	0.4	1.08	<1	2.9
933126	Drill Core	0.031	5	6	0.23	187	<0.001	5	0.42	0.043	0.31	<0.1	0.25	3.7	0.3	0.67	<1	1.3
933127	Drill Core	0.027	3	4	0.06	80	<0.001	2	0.42	0.060	0.25	<0.1	0.07	2.0	<0.1	0.47	<1	0.9
933128	Drill Core	0.019	8	4	0.04	49	<0.001	2	0.50	0.071	0.31	<0.1	0.07	1.8	0.1	0.22	<1	0.7
933129	Drill Core	0.014	5	6	0.15	199	<0.001	2	0.56	0.057	0.37	0.1	0.05	2.7	0.2	0.45	1	1.2
933130	Drill Core	0.029	2	4	0.33	105	<0.001	2	0.56	0.040	0.35	<0.1	0.05	3.7	0.2	0.63	1	0.5
933131	Drill Core	0.084	6	3	0.78	97	0.003	2	0.54	0.036	0.35	<0.1	0.09	5.8	0.3	0.80	2	1.5
933132	Drill Core	0.026	6	5	0.48	230	0.003	2	1.09	0.051	0.46	<0.1	0.04	4.7	0.3	0.43	3	0.8
933133	Drill Core	0.022	5	2	0.31	181	<0.001	1	0.62	0.040	0.46	<0.1	0.04	2.6	0.3	0.47	2	<0.5
933134	Drill Core	0.163	13	7	1.58	59	0.127	1	2.45	0.169	0.27	0.1	0.06	6.9	0.2	1.49	8	3.6
933135	Drill Core	0.060	6	6	0.47	127	0.004	2	1.39	0.049	0.43	<0.1	0.02	5.7	0.3	0.83	4	1.5
933136	Drill Core	0.026	6	4	0.35	79	0.001	2	0.90	0.050	0.41	<0.1	0.02	4.8	0.3	0.70	2	1.5
933137	Drill Core	0.019	17	4	0.48	56	0.002	1	1.06	0.045	0.35	<0.1	0.02	4.7	0.3	0.58	3	1.0
933138	Drill Core	0.024	5	5	0.56	81	0.002	2	1.31	0.062	0.42	<0.1	0.02	6.5	0.3	0.81	4	1.4
933139	Drill Core	0.023	7	4	0.50	117	0.002	2	1.07	0.054	0.35	<0.1	0.02	5.0	0.2	0.64	3	0.8
933140	Drill Core	0.029	5	8	0.62	112	0.003	2	1.45	0.066	0.37	<0.1	0.02	6.5	0.3	0.84	5	1.4
933141	Drill Core	0.121	14	7	0.66	80	0.005	2	1.08	0.060	0.26	<0.1	0.07	5.6	0.2	1.00	5	2.1
933142	Drill Core	0.164	25	4	0.92	115	0.011	2	1.34	0.049	0.17	<0.1	0.09	3.0	0.2	0.95	7	2.0
933143	Drill Core	0.164	28	4	0.85	79	0.010	2	1.08	0.044	0.17	<0.1	0.09	3.1	0.1	1.16	6	2.3
933144	Drill Core	0.179	21	3	0.70	60	0.002	2	0.85	0.047	0.24	<0.1	0.06	3.4	0.1	1.08	4	2.9
933145	Drill Core	0.161	14	3	0.63	78	<0.001	3	0.52	0.034	0.24	<0.1	0.08	3.4	0.2	1.00	2	2.2
933146	Drill Core	0.162	23	3	0.89	57	0.002	3	1.10	0.057	0.28	<0.1	0.04	3.3	0.2	1.41	5	2.6
933147	Drill Core	0.167	24	2	0.88	61	0.001	1	1.02	0.051	0.22	<0.1	0.04	2.8	0.2	1.55	4	3.2
933148	Drill Core	0.166	23	3	0.78	50	0.002	2	1.08	0.049	0.28	<0.1	0.04	3.3	0.2	1.44	4	2.7

This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**

110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo

Report Date: October 17, 2008

Page: 3 of 3 Part 1

CERTIFICATE OF ANALYSIS

SMI08000963.1

Method	Analyte	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca
Unit		kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%
MDL		0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01
933149	Drill Core	6.71	41.8	2680	13.9	38	0.9	3.8	20.3	288	2.70	68.1	3.7	134.4	8.7	142	0.3	11.5	0.2	15	3.10
933150	Rock Pulp	0.05	7.1	3049	15.3	125	0.5	132.1	13.9	785	5.72	13.9	0.2	226.8	1.6	178	0.6	5.9	0.5	54	2.75
933151	Drill Core	7.69	15.1	870.1	11.8	48	0.3	3.7	18.0	284	3.12	5.2	4.0	57.8	11.1	481	0.2	1.4	0.2	46	2.54
933152	Drill Core	7.86	35.1	1120	13.9	41	0.4	3.1	14.2	258	2.51	6.6	3.8	101.6	10.2	141	0.3	2.1	0.2	21	2.50
933153	Drill Core	6.21	18.4	1025	17.3	55	0.4	4.3	15.9	325	3.20	8.0	2.8	72.5	11.8	211	0.3	2.1	0.3	49	2.40
933154	Drill Core	6.35	31.4	1575	10.7	46	0.6	5.5	17.2	400	3.88	1.6	0.6	103.2	1.6	171	0.2	1.2	0.2	57	1.21
933155	Drill Core	6.74	33.3	789.9	8.2	46	0.3	7.2	17.9	732	4.56	0.9	0.4	55.3	1.0	58	0.2	0.6	0.2	71	1.37
933156	Drill Core	5.72	20.2	751.0	11.3	52	0.3	6.7	19.0	793	4.62	1.3	0.3	41.2	0.9	46	0.2	0.6	0.2	78	1.24
933157	Drill Core	6.74	28.6	1350	13.4	55	0.5	8.6	25.7	667	5.47	1.7	0.3	67.1	0.4	72	0.2	0.6	0.2	101	1.37
933158	Drill Core	6.13	26.6	555.6	5.5	41	0.2	6.9	14.6	806	4.65	2.6	0.4	33.2	0.5	113	0.1	0.7	0.2	46	1.26
933159	Drill Core	7.16	72.8	892.1	9.4	45	0.3	8.8	20.4	818	4.78	2.4	1.4	54.1	0.5	161	0.2	0.7	0.2	91	1.51
933160	Drill Core	5.42	40.3	713.6	6.1	40	0.3	6.9	16.0	674	4.39	1.0	0.2	49.3	0.5	44	0.1	0.2	0.3	90	1.28
933161	Drill Core	8.01	46.9	3153	10.3	40	1.1	9.6	34.8	424	4.61	1.7	0.9	185.1	0.6	99	0.3	0.2	0.3	83	2.70
933162	Drill Core	8.00	62.7	1206	10.4	42	0.5	6.6	18.9	724	3.90	2.2	3.9	99.0	1.1	95	0.2	0.5	0.2	77	1.59
933163	Drill Core	7.81	21.1	389.8	10.4	37	0.2	6.5	15.9	756	3.86	1.3	0.3	30.4	1.1	42	0.1	0.5	0.2	64	1.45
933164	Drill Core	7.56	22.0	1026	11.2	51	0.4	10.2	33.5	390	4.84	2.1	0.5	30.4	0.6	61	0.2	0.1	0.3	138	2.17
933165	Drill Core	7.64	19.1	917.1	11.0	51	0.3	10.4	27.8	436	4.63	8.2	0.5	30.7	0.4	93	0.2	0.3	0.2	128	2.92
933166	Drill Core	6.43	43.9	1921	25.5	64	1.7	14.7	38.1	1729	6.40	35.9	0.3	192.0	0.3	46	0.3	1.1	1.0	61	3.18
933167	Drill Core	8.03	28.5	1468	11.8	46	0.5	9.5	26.8	382	4.22	1.8	1.6	94.1	0.4	59	0.2	0.2	0.2	116	2.17
933168	Drill Core	8.79	38.2	801.5	11.3	28	0.3	5.3	10.9	324	1.82	2.4	0.6	56.4	1.0	112	0.2	0.1	0.2	43	2.81



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
 Report Date: October 17, 2008

Page: 3 of 3 Part 2

CERTIFICATE OF ANALYSIS

SMI08000963.1

Method	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se	
Unit	%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
MDL	0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5	
933149	Drill Core	0.156	17	5	0.45	70	<0.001	3	0.58	0.036	0.28	<0.1	0.05	2.8	0.2	1.21	1	3.4
933150	Rock Pulp	0.115	5	164	1.10	24	0.001	5	1.01	0.049	0.36	0.4	1.23	6.5	0.2	2.85	3	8.3
933151	Drill Core	0.162	30	3	0.90	70	0.003	2	1.32	0.047	0.19	<0.1	0.06	2.8	0.1	1.01	7	2.1
933152	Drill Core	0.163	25	3	0.62	76	0.001	2	0.81	0.035	0.22	0.2	0.05	2.4	0.2	0.81	3	2.0
933153	Drill Core	0.172	29	6	0.92	58	0.003	1	1.32	0.056	0.18	1.2	0.06	3.3	0.1	1.02	6	2.1
933154	Drill Core	0.037	9	7	0.74	143	0.034	1	1.48	0.059	0.27	0.1	0.03	6.0	0.2	0.66	6	1.1
933155	Drill Core	0.123	8	11	0.65	93	0.028	2	1.76	0.053	0.30	<0.1	0.01	6.4	0.3	0.64	7	0.6
933156	Drill Core	0.041	6	14	0.67	110	0.023	2	1.88	0.055	0.37	<0.1	0.02	7.3	0.4	0.78	7	0.9
933157	Drill Core	0.056	5	21	0.71	107	0.045	2	1.99	0.066	0.36	0.1	0.02	8.9	0.3	1.26	7	1.7
933158	Drill Core	0.042	4	7	0.61	174	0.005	2	1.37	0.047	0.49	<0.1	0.02	6.1	0.4	0.51	4	0.7
933159	Drill Core	0.075	9	16	0.71	98	0.016	2	1.95	0.057	0.39	<0.1	0.02	8.1	0.3	0.95	7	1.4
933160	Drill Core	0.072	4	10	0.79	182	0.042	1	1.87	0.058	0.40	<0.1	0.04	7.8	0.4	0.57	7	0.8
933161	Drill Core	0.119	11	13	0.54	41	0.029	2	1.18	0.046	0.21	0.1	0.02	6.9	0.2	2.58	6	4.7
933162	Drill Core	0.059	7	8	0.68	109	0.010	2	1.62	0.061	0.42	<0.1	0.02	6.7	0.4	1.02	6	1.5
933163	Drill Core	0.057	5	8	0.68	148	0.046	2	1.89	0.050	0.49	<0.1	0.01	6.7	0.4	0.49	6	0.8
933164	Drill Core	0.085	6	20	0.91	66	0.156	2	1.86	0.070	0.24	0.4	0.03	11.5	0.2	2.39	7	3.8
933165	Drill Core	0.093	6	24	1.16	29	0.069	1	1.86	0.077	0.19	0.2	0.02	10.4	0.2	2.27	7	3.6
933166	Drill Core	0.062	6	11	0.55	23	0.008	3	1.55	0.029	0.25	0.1	0.04	7.3	0.4	4.22	5	4.9
933167	Drill Core	0.117	7	17	0.60	40	0.077	2	1.38	0.057	0.14	0.3	0.02	8.5	0.2	2.18	6	3.6
933168	Drill Core	0.129	12	7	0.32	84	0.004	2	0.92	0.054	0.25	0.1	0.02	4.5	0.2	1.03	3	1.6

QUALITY CONTROL REPORT

SMI08000963.1

Method	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
Unit	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	
MDL	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	
Pulp Duplicates																					
933162	Drill Core	8.00	62.7	1206	10.4	42	0.5	6.6	18.9	724	3.90	2.2	3.9	99.0	1.1	95	0.2	0.5	0.2	77	1.59
REP 933162	QC		62.8	1200	10.5	44	0.5	6.8	17.8	772	3.89	2.4	4.3	70.8	1.1	98	0.2	0.6	0.2	78	1.60
Core Reject Duplicates																					
933130	Drill Core	6.93	43.4	780.7	27.6	29	0.5	4.2	9.5	560	1.85	229.4	0.4	45.4	0.6	44	0.1	24.8	0.2	9	1.28
DUP 933130	QC		44.6	798.1	28.4	31	0.5	4.7	10.3	545	1.87	251.3	0.6	42.1	0.6	44	0.2	16.9	0.2	8	1.30
933165	Drill Core	7.64	19.1	917.1	11.0	51	0.3	10.4	27.8	436	4.63	8.2	0.5	30.7	0.4	93	0.2	0.3	0.2	128	2.92
DUP 933165	QC		19.6	994.2	11.0	47	0.3	9.5	30.1	454	4.76	7.5	0.5	28.0	0.3	78	<0.1	0.3	0.2	117	3.15
Reference Materials																					
STD DS7	Standard		20.4	114.2	80.6	393	0.8	53.7	9.6	612	2.24	51.5	5.5	67.3	4.8	76	6.5	7.3	5.2	76	0.93
STD DS7	Standard		21.8	107.9	77.5	405	0.8	52.9	9.3	588	2.25	52.1	5.4	95.2	5.1	81	6.3	7.2	5.2	77	0.93
STD DS7	Standard		20.5	102.2	73.3	391	0.8	54.4	9.1	599	2.31	50.5	5.3	63.7	4.9	71	6.1	6.1	4.7	77	0.95
STD DS7	Standard		20.3	108.4	74.8	420	0.8	56.1	9.1	627	2.41	50.3	5.4	77.2	5.1	73	6.2	5.9	4.7	81	1.03
STD DS7	Standard		18.1	112.6	73.8	391	0.8	53.0	9.9	599	2.33	58.2	5.5	71.2	5.0	77	7.7	5.7	5.0	79	0.95
STD DS7	Standard		20.8	121.6	78.7	427	0.9	55.7	10.0	630	2.36	60.9	5.7	78.3	5.3	83	7.7	6.4	5.4	82	0.99
STD DS7 Expected			20.9	109	70.6	411	0.9	56	9.7	627	2.39	48.2	4.9	70	4.4	69	6.4	5.9	4.5	86	0.93
BLK	Blank		<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01
BLK	Blank		<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01
BLK	Blank		<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01
Prep Wash																					
G1	Prep Blank	<0.01	1.0	2.1	2.9	46	<0.1	4.8	4.4	529	1.87	<0.5	1.7	<0.5	4.1	60	<0.1	<0.1	<0.1	36	0.65
G1	Prep Blank	<0.01	1.1	2.4	2.8	47	<0.1	4.7	4.7	554	1.93	<0.5	2.0	0.7	4.0	66	<0.1	<0.1	<0.1	37	0.52

QUALITY CONTROL REPORT

SMI08000963.1

Method		1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte		P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
Unit		%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm
MDL		0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5
Pulp Duplicates																		
933162	Drill Core	0.059	7	8	0.68	109	0.010	2	1.62	0.061	0.42	<0.1	0.02	6.7	0.4	1.02	6	1.5
REP 933162	QC	0.059	7	8	0.69	134	0.011	2	1.66	0.056	0.48	<0.1	0.03	6.9	0.4	1.03	6	1.7
Core Reject Duplicates																		
933130	Drill Core	0.029	2	4	0.33	105	<0.001	2	0.56	0.040	0.35	<0.1	0.05	3.7	0.2	0.63	1	0.5
DUP 933130	QC	0.033	2	2	0.32	102	<0.001	2	0.44	0.039	0.36	<0.1	0.04	3.9	0.2	0.65	1	1.0
933165	Drill Core	0.093	6	24	1.16	29	0.069	1	1.86	0.077	0.19	0.2	0.02	10.4	0.2	2.27	7	3.6
DUP 933165	QC	0.080	5	23	1.16	21	0.055	2	1.92	0.074	0.19	0.1	0.03	10.3	0.2	2.42	6	4.4
Reference Materials																		
STD DS7	Standard	0.070	14	183	1.01	375	0.127	34	0.94	0.083	0.37	4.0	0.20	2.4	4.1	0.19	5	4.3
STD DS7	Standard	0.078	14	178	1.01	377	0.128	39	0.98	0.083	0.42	3.7	0.20	2.2	4.1	0.19	5	4.2
STD DS7	Standard	0.072	13	177	1.02	382	0.127	40	1.00	0.080	0.41	4.1	0.18	2.6	4.5	0.18	4	4.3
STD DS7	Standard	0.074	14	169	1.05	401	0.124	40	1.04	0.082	0.42	3.9	0.19	2.5	4.5	0.19	5	4.4
STD DS7	Standard	0.083	13	161	1.03	361	0.115	39	0.99	0.088	0.44	3.9	0.19	2.5	4.1	0.18	5	3.9
STD DS7	Standard	0.085	15	178	1.05	392	0.128	42	1.01	0.089	0.46	4.0	0.20	2.6	4.6	0.19	5	4.0
STD DS7 Expected		0.08	13	163	1.05	370	0.124	39	0.959	0.073	0.44	3.8	0.2	2.5	4.2	0.21	4.6	3.5
BLK	Blank	<0.001	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
BLK	Blank	<0.001	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
BLK	Blank	<0.001	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
Prep Wash																		
G1	Prep Blank	0.080	8	12	0.60	226	0.125	<1	0.96	0.066	0.52	1.3	<0.01	2.1	0.3	<0.05	5	<0.5
G1	Prep Blank	0.086	7	20	0.61	255	0.140	<1	0.95	0.078	0.54	0.8	<0.01	2.2	0.3	<0.05	5	<0.5



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.

Vancouver BC V6C 1Z7 Canada

Submitted By:

Glen Garratt

Receiving Lab:

Canada-Smithers

Received:

September 26, 2008

Report Date:

October 22, 2008

Page:

1 of 3

CERTIFICATE OF ANALYSIS

SMI08000981.1

CLIENT JOB INFORMATION

Project: Zymo
Shipment ID: zy-co-08-05
P.O. Number
Number of Samples: 56

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
DISP-RJT Dispose of Reject After 90 days

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Mincord Exploration Consultants Ltd.
110 - 325 Howe St.
Vancouver BC V6C 1Z7
Canada

CC: Bob Johnston

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status
R150	54	Crush split and pulverize drill core to 200 mesh		
1DX15	56	1:1:1 Aqua Regia digestion ICP-MS analysis	15	Completed

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only. All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.

** asterisk indicates that an analytical result could not be provided due to unusually high levels of interference from other elements.



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.

110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo

Report Date: October 22, 2008

Page: 2 of 3 Part 1

CERTIFICATE OF ANALYSIS

SMI08000981.1

Method Analyte Unit MDL	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%
	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	
933169	Drill Core	2.81	11.0	3137	14.9	54	1.0	2.8	10.2	1198	3.67	51.7	3.0	206.4	7.4	183	0.4	13.1	0.2	27	3.94
933170	Drill Core	7.38	2.6	1558	17.1	52	0.7	2.3	10.5	1020	2.98	27.5	5.2	118.4	15.5	247	0.2	26.5	0.2	20	2.78
933171	Drill Core	6.32	9.5	3598	17.3	54	2.3	2.8	10.3	826	3.89	71.9	3.8	282.8	11.1	130	0.1	160.8	0.4	20	2.42
933172	Drill Core	6.80	10.4	2978	24.2	103	1.7	2.5	11.0	758	3.34	15.2	3.4	212.4	12.2	448	0.7	19.3	0.3	18	2.11
933173	Drill Core	7.22	9.3	4726	14.2	38	2.1	3.6	11.8	528	3.44	12.6	3.4	345.8	12.4	442	0.3	15.0	0.4	28	2.03
933174	Drill Core	7.86	3.7	5091	11.4	84	1.7	5.7	15.0	1010	4.63	4.7	1.8	409.9	6.9	1256	0.5	5.2	0.2	74	2.00
933175	Drill Core	6.24	11.6	2993	6.4	49	0.8	5.3	11.4	396	3.40	10.5	0.9	223.1	4.1	490	0.2	9.4	0.2	59	1.63
933176	Drill Core	7.22	11.3	6737	16.6	49	2.0	3.8	13.1	997	4.63	17.0	1.4	602.5	6.0	229	1.2	6.0	0.3	24	3.20
933177	Drill Core	6.19	55.9	5912	9.5	38	1.8	3.7	11.8	499	4.90	21.0	2.4	463.5	3.5	128	0.2	2.4	0.3	29	1.74
933178	Drill Core	6.59	87.4	5317	10.2	50	1.6	2.5	11.5	539	5.18	9.3	4.8	367.4	12.1	322	0.3	4.9	0.2	33	2.46
933179	Drill Core	6.19	40.8	8259	7.2	38	2.5	3.2	13.8	321	6.29	51.7	1.3	584.0	7.9	133	0.2	9.9	0.3	39	1.05
933180	Rock Pulp	0.09	7.6	3071	15.1	128	0.6	146.9	14.3	826	5.96	12.8	0.2	263.4	1.5	174	0.6	8.7	0.5	57	2.85
933181	Drill Core	8.05	55.2	7968	6.3	39	2.4	3.3	13.2	322	5.93	4.0	2.6	560.6	10.0	687	0.1	2.1	0.3	48	1.25
933182	Drill Core	6.75	115.2	5410	7.8	43	1.7	3.2	12.5	444	7.05	13.3	2.3	420.9	9.9	148	0.3	5.7	0.2	35	1.62
933183	Drill Core	6.37	21.0	7518	15.0	63	3.4	3.2	12.6	1014	7.84	12.6	1.3	529.3	5.9	106	0.3	13.7	0.4	27	1.67
933184	Drill Core	6.73	19.2	8960	14.3	55	4.4	3.6	13.0	955	8.10	6.7	1.3	625.5	6.5	63	0.3	4.8	0.5	29	1.09
933185	Drill Core	7.03	43.6	6460	8.5	55	2.7	3.3	16.0	560	8.22	146.5	1.2	463.5	6.4	72	0.3	53.5	0.3	34	1.27
933186	Drill Core	6.97	19.1	9643	11.5	50	3.2	4.6	17.3	432	8.95	73.0	0.9	842.5	5.6	56	0.2	19.0	0.4	38	0.67
933187	Drill Core	7.53	27.0	8708	10.2	43	3.0	3.9	14.1	452	8.70	128.0	1.0	730.0	6.3	51	0.2	4.2	0.4	42	0.73
933188	Drill Core	8.48	16.8	>10000	9.7	51	4.8	4.9	17.0	396	9.10	19.1	0.8	1093	5.3	69	0.3	9.5	0.7	59	0.83
933189	Drill Core	6.26	42.6	9767	20.8	98	4.2	4.5	18.0	633	8.38	34.8	0.9	854.7	5.5	69	0.6	6.7	0.6	40	1.23
933190	Drill Core	7.01	64.2	>10000	18.0	82	3.9	4.6	17.5	762	8.23	13.6	1.4	740.2	7.3	67	0.4	20.6	0.7	43	1.30
933191	Drill Core	7.31	78.4	6031	9.2	45	2.3	3.0	19.7	473	6.43	6.8	1.9	472.6	12.0	175	0.2	3.2	0.3	40	1.35
933192	Drill Core	8.59	163.0	7957	12.0	63	3.1	3.6	19.4	726	7.67	6.9	1.6	576.7	9.2	108	0.3	4.6	0.4	47	1.23
933193	Drill Core	6.43	23.4	7843	9.0	51	2.6	3.2	13.7	577	8.79	4.7	1.4	646.3	9.0	72	0.2	5.7	0.4	66	1.28
933194	Drill Core	6.86	22.8	4867	8.4	47	1.9	3.0	11.0	592	6.04	11.6	2.0	317.6	10.9	116	0.1	43.5	0.3	41	1.40
933195	Drill Core	6.35	82.2	5128	8.8	45	1.2	2.9	11.5	500	6.26	19.8	1.9	353.5	10.6	88	0.1	47.5	0.3	33	1.27
933196	Drill Core	8.28	24.2	5891	11.2	59	1.8	2.7	14.0	574	7.23	31.2	1.7	419.7	9.6	58	0.3	52.2	0.3	34	1.06
933197	Drill Core	7.10	6.8	5316	7.9	54	2.1	2.8	12.2	490	7.34	41.2	1.6	369.3	10.7	49	0.2	58.2	0.3	40	1.09
933198	Drill Core	6.85	22.7	3278	9.1	52	1.1	3.0	11.7	649	5.52	39.9	2.8	242.1	12.4	85	0.2	50.7	0.2	36	1.97

This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
 Report Date: October 22, 2008

Page: 2 of 3 Part 2

CERTIFICATE OF ANALYSIS

SMI08000981.1

Method	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se	
Unit	%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
MDL	0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5	
933169	Drill Core	0.107	10	4	0.82	168	<0.001	3	0.36	0.007	0.27	0.6	0.14	3.6	0.3	0.93	<1	1.6
933170	Drill Core	0.123	19	3	0.58	107	<0.001	4	0.40	0.010	0.29	0.1	0.29	3.2	0.3	1.03	1	1.3
933171	Drill Core	0.089	9	5	0.62	138	<0.001	3	0.34	0.004	0.27	0.6	0.23	2.6	0.3	0.95	1	2.0
933172	Drill Core	0.107	11	5	0.58	126	<0.001	4	0.34	0.010	0.29	0.1	0.37	2.8	0.2	0.98	1	1.8
933173	Drill Core	0.104	11	8	0.61	93	0.002	2	0.45	0.019	0.28	0.4	0.25	3.1	0.2	1.01	2	2.2
933174	Drill Core	0.152	14	6	1.21	196	0.056	2	1.06	0.036	0.47	<0.1	0.64	8.0	0.4	0.71	5	2.9
933175	Drill Core	0.097	8	11	0.90	317	0.045	3	0.75	0.029	0.49	0.4	0.25	7.7	0.4	0.51	3	1.2
933176	Drill Core	0.106	7	5	0.93	113	0.002	3	0.36	0.008	0.30	<0.1	0.36	4.3	0.2	1.36	1	4.9
933177	Drill Core	0.035	4	7	0.48	96	<0.001	3	0.29	0.010	0.29	0.2	0.38	4.1	0.3	0.91	1	3.5
933178	Drill Core	0.115	16	6	0.63	210	0.001	3	0.34	0.010	0.26	0.1	0.40	3.8	0.2	0.78	2	2.6
933179	Drill Core	0.059	5	12	0.41	109	<0.001	3	0.29	0.009	0.22	0.2	0.35	2.0	0.1	1.15	2	4.5
933180	Rock Pulp	0.110	6	179	1.14	38	0.002	6	1.16	0.053	0.37	0.4	1.32	6.8	0.2	2.84	3	9.2
933181	Drill Core	0.090	9	7	0.47	97	0.003	2	0.34	0.015	0.22	0.1	0.54	2.5	0.1	1.19	3	4.9
933182	Drill Core	0.095	9	9	0.53	141	<0.001	4	0.36	0.013	0.29	0.1	0.36	3.0	0.1	0.85	2	3.1
933183	Drill Core	0.041	3	8	0.72	108	<0.001	3	0.22	0.004	0.22	<0.1	0.29	1.6	0.2	1.18	1	4.6
933184	Drill Core	0.041	3	15	0.46	90	<0.001	4	0.23	0.005	0.23	0.2	0.33	1.7	0.1	1.38	2	5.5
933185	Drill Core	0.047	4	10	0.43	119	<0.001	3	0.21	0.005	0.21	0.1	0.52	1.8	0.1	1.18	2	3.6
933186	Drill Core	0.035	3	19	0.33	84	<0.001	2	0.19	0.008	0.20	0.6	0.61	1.7	<0.1	1.18	2	7.3
933187	Drill Core	0.035	3	10	0.37	87	<0.001	3	0.21	0.005	0.18	0.3	0.56	1.4	0.2	1.45	2	4.7
933188	Drill Core	0.024	3	18	0.39	38	<0.001	3	0.19	0.007	0.17	0.3	0.57	1.2	0.1	1.70	3	9.1
933189	Drill Core	0.029	3	10	0.45	45	<0.001	3	0.20	0.005	0.20	0.2	0.48	1.3	0.2	2.07	2	7.2
933190	Drill Core	0.038	5	12	0.48	63	0.001	2	0.20	0.005	0.22	<0.1	0.47	1.6	0.2	1.73	1	7.3
933191	Drill Core	0.091	10	11	0.42	101	0.001	3	0.28	0.013	0.23	<0.1	0.22	2.5	0.1	1.09	2	5.2
933192	Drill Core	0.047	7	10	0.36	83	0.001	2	0.21	0.008	0.22	0.2	0.24	1.7	0.1	1.68	2	6.3
933193	Drill Core	0.053	6	11	0.41	120	0.001	3	0.29	0.009	0.21	0.2	0.28	2.0	0.1	1.02	3	4.4
933194	Drill Core	0.080	11	7	0.44	204	0.002	3	0.30	0.011	0.25	0.1	0.18	2.4	0.2	0.66	2	3.2
933195	Drill Core	0.073	10	11	0.40	209	<0.001	5	0.30	0.012	0.27	<0.1	0.18	2.5	0.1	0.64	2	3.4
933196	Drill Core	0.062	6	9	0.38	125	<0.001	3	0.27	0.007	0.25	0.2	0.41	1.9	0.2	1.05	2	4.9
933197	Drill Core	0.064	5	12	0.39	123	<0.001	4	0.25	0.008	0.23	0.1	0.32	2.1	0.1	0.83	2	4.2
933198	Drill Core	0.116	14	7	0.61	256	0.001	4	0.24	0.011	0.22	<0.1	0.45	3.5	0.1	0.50	1	2.6

This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**

110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo

Report Date: October 22, 2008

Page: 3 of 3 Part 1

CERTIFICATE OF ANALYSIS

SMI08000981.1

Method	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
Unit	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	
MDL	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	
933199	Drill Core	6.52	3.7	1352	8.4	55	0.4	3.2	10.7	742	5.18	30.0	3.6	109.3	13.3	146	0.2	41.4	0.2	62	2.97
933200	Drill Core	6.67	3.2	1491	10.5	35	0.6	2.1	8.3	428	3.36	86.1	4.2	94.6	15.5	107	0.2	49.2	0.2	20	2.16
933201	Drill Core	7.26	4.4	1093	7.4	33	0.5	2.1	7.1	495	3.51	47.8	3.7	88.1	14.8	155	0.1	11.8	0.1	22	2.47
933202	Drill Core	5.57	1.4	669.5	6.0	30	0.3	2.0	5.7	434	3.34	10.4	3.2	54.1	14.9	741	0.1	14.0	0.1	21	2.61
933203	Drill Core	7.12	2.4	975.7	9.2	36	0.4	2.3	6.4	704	3.86	25.3	3.4	59.2	14.5	163	0.1	4.9	0.1	28	2.48
933204	Drill Core	6.81	4.6	934.3	10.0	42	0.3	2.5	6.9	700	3.33	11.2	4.4	81.9	14.6	603	0.1	1.6	0.1	36	2.43
933205	Drill Core	6.68	4.7	483.0	16.7	54	0.3	2.1	6.1	1013	2.34	39.1	8.0	36.8	17.0	276	0.2	2.5	0.5	20	3.09
933206	Drill Core	7.24	3.5	793.0	9.6	33	0.2	1.9	6.8	535	2.37	14.3	5.8	44.2	18.3	915	0.1	0.9	0.1	23	2.60
933207	Drill Core	6.17	1473	>10000	14.3	65	4.5	5.7	18.0	578	4.40	167.5	5.0	817.4	16.2	338	0.6	1.7	0.5	29	4.42
933208	Drill Core	6.95	2.9	650.4	6.2	24	0.2	1.6	5.3	401	2.01	3.4	5.8	36.2	18.7	792	0.1	0.2	<0.1	28	2.52
933209	Drill Core	6.64	10.8	2216	8.4	38	0.6	2.4	9.0	517	3.61	8.1	3.8	156.4	14.3	698	0.2	0.5	0.2	34	3.13
933210	Rock Pulp	0.09	7.6	3150	15.1	130	0.6	117.8	13.9	829	5.50	12.0	0.2	263.3	1.5	180	0.6	8.2	0.4	52	2.82
933211	Drill Core	5.79	6.2	2552	11.9	36	0.7	2.4	8.6	500	3.85	230.9	3.5	237.8	12.0	260	0.1	9.7	0.2	18	4.15
933212	Drill Core	6.15	29.2	1807	18.3	44	0.6	2.8	7.7	438	2.52	319.7	5.1	144.0	13.2	177	0.2	3.7	0.2	8	4.51
933213	Drill Core	6.35	26.3	1415	32.6	99	0.5	1.8	6.3	409	2.26	81.8	6.5	113.6	14.9	2877	0.5	3.1	0.3	14	2.92
933214	Drill Core	6.65	5.6	1979	7.4	23	0.7	2.7	7.8	265	2.34	107.2	6.2	128.9	13.4	1274	0.1	3.7	0.1	13	2.73
933215	Drill Core	5.68	8.1	1511	6.7	17	0.5	2.0	6.2	227	1.94	15.4	6.3	95.4	14.0	4226	<0.1	4.1	0.1	13	2.58
933216	Drill Core	6.87	47.9	742.8	7.4	18	0.3	2.0	7.8	264	2.40	33.1	6.4	35.3	13.1	2382	<0.1	1.5	<0.1	16	3.22
933217	Drill Core	6.71	28.7	2036	16.6	48	0.7	6.8	12.3	479	3.76	33.3	0.9	96.3	1.5	249	0.3	3.5	0.2	16	3.82
933218	Drill Core	6.27	26.3	1881	12.7	41	0.7	6.8	10.7	394	3.21	245.7	2.5	125.9	7.0	120	<0.1	104.9	0.2	17	2.42
933219	Drill Core	6.87	40.5	2826	15.1	60	0.9	22.2	11.2	522	3.30	29.8	3.6	192.3	9.4	101	0.3	4.0	0.3	18	2.94
933220	Drill Core	7.64	10.8	1170	9.3	19	0.4	2.6	6.5	339	2.54	40.6	5.1	68.9	14.4	159	0.1	20.7	0.1	10	2.84
933221	Drill Core	5.76	14.5	1026	10.1	24	0.4	2.2	9.0	405	2.45	21.4	5.7	56.0	13.1	872	<0.1	15.2	0.1	21	3.25
933222	Drill Core	5.20	43.5	1097	10.7	35	0.4	6.2	10.1	471	2.21	5.0	2.7	49.5	5.4	370	0.2	1.2	0.2	30	2.20
933223	Drill Core	7.69	66.5	2300	12.4	49	0.8	10.8	16.5	587	4.06	4.7	0.6	153.0	1.2	429	0.3	0.7	0.2	47	2.25
933224	Drill Core	7.00	43.4	603.1	17.9	58	0.3	7.8	7.5	600	2.07	8.7	0.7	55.8	1.5	92	0.2	0.3	0.2	39	1.56



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
 Report Date: October 22, 2008

Page: 3 of 3 Part 2

CERTIFICATE OF ANALYSIS

SMI08000981.1

Method	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se	
Unit	%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
MDL	0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5	
933199	Drill Core	0.139	19	5	0.81	326	0.001	5	0.30	0.015	0.24	<0.1	0.91	5.2	0.1	0.37	2	1.1
933200	Drill Core	0.124	13	4	0.50	151	<0.001	6	0.29	0.009	0.24	<0.1	1.41	3.4	0.1	0.87	<1	1.4
933201	Drill Core	0.124	13	5	0.49	477	<0.001	8	0.31	0.014	0.28	<0.1	0.48	3.5	0.1	0.31	<1	0.8
933202	Drill Core	0.120	14	5	0.53	607	0.003	6	0.31	0.021	0.28	<0.1	0.10	3.6	0.1	0.22	<1	0.9
933203	Drill Core	0.105	13	6	0.60	394	<0.001	4	0.32	0.019	0.26	<0.1	0.12	3.1	0.1	0.33	<1	1.0
933204	Drill Core	0.125	24	5	0.55	427	0.002	4	0.37	0.044	0.27	0.1	1.26	4.3	0.1	0.35	2	1.0
933205	Drill Core	0.122	26	4	0.67	340	<0.001	7	0.37	0.042	0.26	1.4	0.88	3.9	0.2	0.46	<1	0.9
933206	Drill Core	0.124	24	5	0.56	376	0.003	5	0.35	0.040	0.25	<0.1	1.35	3.9	0.1	0.39	1	1.1
933207	Drill Core	0.234	51	3	0.88	68	0.004	5	0.31	0.023	0.25	0.2	2.07	3.7	0.6	2.20	1	9.5
933208	Drill Core	0.124	27	4	0.42	637	0.004	3	0.31	0.036	0.21	<0.1	0.21	3.9	<0.1	0.23	1	0.7
933209	Drill Core	0.135	18	4	0.54	321	0.002	3	0.30	0.029	0.24	<0.1	0.35	3.5	0.1	0.58	1	1.6
933210	Rock Pulp	0.121	5	147	1.12	53	0.002	5	1.01	0.055	0.35	0.4	1.27	6.5	0.2	2.92	2	8.5
933211	Drill Core	0.127	13	<1	0.51	215	<0.001	5	0.31	0.022	0.27	<0.1	0.52	3.0	0.2	0.75	<1	2.2
933212	Drill Core	0.121	9	2	0.39	289	0.001	7	0.36	0.018	0.31	0.1	0.84	2.4	0.2	0.64	<1	1.7
933213	Drill Core	0.119	12	3	0.53	376	0.001	6	0.39	0.024	0.30	0.4	1.03	2.9	0.2	0.60	1	1.5
933214	Drill Core	0.120	10	3	0.42	304	<0.001	6	0.37	0.026	0.27	<0.1	0.31	2.7	0.2	0.52	<1	1.9
933215	Drill Core	0.128	15	3	0.45	410	0.002	6	0.37	0.028	0.28	<0.1	0.31	2.6	0.2	0.64	1	1.5
933216	Drill Core	0.138	20	3	0.52	252	0.004	3	0.42	0.034	0.27	0.2	0.25	3.4	0.2	0.82	1	1.0
933217	Drill Core	0.084	6	3	0.88	212	0.001	3	0.32	0.033	0.25	<0.1	0.40	6.0	0.2	0.90	1	2.3
933218	Drill Core	0.092	8	3	0.63	298	0.001	5	0.40	0.034	0.29	0.1	0.14	5.1	0.2	0.65	1	1.7
933219	Drill Core	0.082	8	8	0.65	260	0.002	5	0.36	0.036	0.28	<0.1	0.38	4.0	0.2	0.74	<1	2.2
933220	Drill Core	0.135	16	2	0.62	217	0.001	4	0.40	0.039	0.32	<0.1	0.23	2.9	0.2	0.81	<1	1.4
933221	Drill Core	0.142	29	2	0.59	293	0.003	4	0.62	0.049	0.27	<0.1	0.15	2.9	0.2	0.59	2	1.1
933222	Drill Core	0.075	17	8	0.56	277	0.004	3	0.71	0.049	0.25	<0.1	0.18	4.4	0.2	0.75	3	1.3
933223	Drill Core	0.067	9	12	0.68	253	0.008	2	0.98	0.050	0.28	<0.1	0.18	5.1	0.2	0.81	4	1.7
933224	Drill Core	0.064	8	13	0.64	322	0.003	2	1.19	0.060	0.30	<0.1	0.18	5.4	0.3	0.41	5	0.8

QUALITY CONTROL REPORT

SMI08000981.1

Method	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
Unit	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	
MDL	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	
Pulp Duplicates																					
933193	Drill Core	6.43	23.4	7843	9.0	51	2.6	3.2	13.7	577	8.79	4.7	1.4	646.3	9.0	72	0.2	5.7	0.4	66	1.28
REP 933193	QC		21.0	7633	8.8	54	2.6	3.1	13.0	569	8.55	5.0	1.4	635.8	8.8	72	0.1	5.4	0.4	64	1.25
933220	Drill Core	7.64	10.8	1170	9.3	19	0.4	2.6	6.5	339	2.54	40.6	5.1	68.9	14.4	159	0.1	20.7	0.1	10	2.84
REP 933220	QC		11.2	1180	9.1	21	0.4	2.3	6.9	351	2.58	41.2	4.9	66.1	13.6	159	0.1	20.2	0.1	9	2.87
Core Reject Duplicates																					
933195	Drill Core	6.35	82.2	5128	8.8	45	1.2	2.9	11.5	500	6.26	19.8	1.9	353.5	10.6	88	0.1	47.5	0.3	33	1.27
DUP 933195	QC		93.2	5266	9.3	46	1.3	3.0	12.0	542	6.40	20.7	1.9	380.8	10.9	87	0.1	49.8	0.3	32	1.28
Reference Materials																					
STD DS7	Standard		21.2	106.5	73.4	415	0.9	56.7	9.6	641	2.39	52.1	5.3	83.0	4.9	78	6.3	6.3	5.0	86	1.00
STD DS7	Standard		21.0	110.1	71.4	402	0.8	58.3	9.5	632	2.47	52.7	5.3	66.2	4.4	79	6.2	6.3	4.8	84	1.00
STD DS7	Standard		21.0	104.2	72.8	397	0.9	55.5	9.6	602	2.33	54.5	5.3	73.2	4.6	70	6.8	6.2	4.9	78	0.94
STD DS7	Standard		20.8	107.1	68.0	409	0.8	56.0	9.7	640	2.35	54.2	4.9	63.2	4.3	78	6.7	5.9	4.8	78	0.97
STD DS7 Expected			20.9	109	70.6	411	0.9	56	9.7	627	2.39	48.2	4.9	70	4.4	69	6.4	5.9	4.5	86	0.93
BLK	Blank		<0.1	1.3	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01
BLK	Blank		<0.1	0.5	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01
Prep Wash																					
G1	Prep Blank	<0.01	0.6	6.2	2.4	49	<0.1	4.6	4.6	572	2.11	<0.5	1.7	<0.5	3.8	61	<0.1	<0.1	0.2	43	0.54
G1	Prep Blank	<0.01	0.4	3.5	2.6	51	<0.1	4.1	4.6	575	1.99	<0.5	1.7	<0.5	4.0	58	<0.1	<0.1	0.1	40	0.54

QUALITY CONTROL REPORT

SMI08000981.1

Method		1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte		P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
Unit		%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm
MDL		0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5
Pulp Duplicates																		
933193	Drill Core	0.053	6	11	0.41	120	0.001	3	0.29	0.009	0.21	0.2	0.28	2.0	0.1	1.02	3	4.4
REP 933193	QC	0.054	6	10	0.40	114	0.001	3	0.28	0.008	0.20	0.2	0.28	1.8	0.1	0.97	3	4.2
933220	Drill Core	0.135	16	2	0.62	217	0.001	4	0.40	0.039	0.32	<0.1	0.23	2.9	0.2	0.81	<1	1.4
REP 933220	QC	0.132	15	2	0.62	201	0.001	4	0.36	0.038	0.31	<0.1	0.23	3.1	0.2	0.82	<1	1.4
Core Reject Duplicates																		
933195	Drill Core	0.073	10	11	0.40	209	<0.001	5	0.30	0.012	0.27	<0.1	0.18	2.5	0.1	0.64	2	3.4
DUP 933195	QC	0.070	10	10	0.41	199	0.001	4	0.31	0.013	0.28	0.1	0.17	2.3	0.1	0.66	2	3.7
Reference Materials																		
STD DS7	Standard	0.079	14	178	1.06	385	0.119	41	1.05	0.090	0.46	3.6	0.22	2.7	4.2	0.20	5	3.5
STD DS7	Standard	0.080	13	173	1.05	374	0.110	41	1.01	0.087	0.44	4.3	0.23	2.6	4.5	0.20	5	4.4
STD DS7	Standard	0.084	12	164	1.03	410	0.114	43	1.00	0.086	0.42	4.1	0.21	2.3	4.4	0.19	5	3.5
STD DS7	Standard	0.085	13	168	1.03	398	0.116	40	1.01	0.087	0.44	4.3	0.18	2.3	4.2	0.19	5	3.9
STD DS7 Expected		0.08	13	163	1.05	370	0.124	39	0.959	0.073	0.44	3.8	0.2	2.5	4.2	0.21	4.6	3.5
BLK	Blank	<0.001	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
BLK	Blank	<0.001	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
Prep Wash																		
G1	Prep Blank	0.083	8	14	0.62	250	0.124	1	0.99	0.071	0.60	0.4	<0.01	2.7	0.4	<0.05	5	<0.5
G1	Prep Blank	0.082	7	11	0.61	248	0.122	<1	0.96	0.060	0.60	0.2	<0.01	2.4	0.4	<0.05	5	<0.5



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.

Vancouver BC V6C 1Z7 Canada

Submitted By:

Glen Garratt

Receiving Lab:

Canada-Smithers

Received:

September 26, 2008

Report Date:

November 06, 2008

Page:

1 of 3

CERTIFICATE OF ANALYSIS

SMI08000981.2

CLIENT JOB INFORMATION

Project: Zymo
Shipment ID: zy-co-08-05
P.O. Number
Number of Samples: 56

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
DISP-RJT Dispose of Reject After 90 days

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Mincord Exploration Consultants Ltd.
110 - 325 Howe St.
Vancouver BC V6C 1Z7
Canada

CC: Bob Johnston

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status
R150	54	Crush split and pulverize drill core to 200 mesh		
1DX15	56	1:1:1 Aqua Regia digestion ICP-MS analysis	15	Completed
7AR	3	1:1:1 Aqua Regia digestion ICP-ES analysis	1	Completed

ADDITIONAL COMMENTS

Ver.2 to include 7AR



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only. All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.

** asterisk indicates that an analytical result could not be provided due to unusually high levels of interference from other elements.



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.

110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo

Report Date: November 06, 2008

Page: 2 of 3 Part 1

CERTIFICATE OF ANALYSIS

SMI08000981.2

Method	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
Unit	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	
MDL	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	
933169	Drill Core	2.81	11.0	3137	14.9	54	1.0	2.8	10.2	1198	3.67	51.7	3.0	206.4	7.4	183	0.4	13.1	0.2	27	3.94
933170	Drill Core	7.38	2.6	1558	17.1	52	0.7	2.3	10.5	1020	2.98	27.5	5.2	118.4	15.5	247	0.2	26.5	0.2	20	2.78
933171	Drill Core	6.32	9.5	3598	17.3	54	2.3	2.8	10.3	826	3.89	71.9	3.8	282.8	11.1	130	0.1	160.8	0.4	20	2.42
933172	Drill Core	6.80	10.4	2978	24.2	103	1.7	2.5	11.0	758	3.34	15.2	3.4	212.4	12.2	448	0.7	19.3	0.3	18	2.11
933173	Drill Core	7.22	9.3	4726	14.2	38	2.1	3.6	11.8	528	3.44	12.6	3.4	345.8	12.4	442	0.3	15.0	0.4	28	2.03
933174	Drill Core	7.86	3.7	5091	11.4	84	1.7	5.7	15.0	1010	4.63	4.7	1.8	409.9	6.9	1256	0.5	5.2	0.2	74	2.00
933175	Drill Core	6.24	11.6	2993	6.4	49	0.8	5.3	11.4	396	3.40	10.5	0.9	223.1	4.1	490	0.2	9.4	0.2	59	1.63
933176	Drill Core	7.22	11.3	6737	16.6	49	2.0	3.8	13.1	997	4.63	17.0	1.4	602.5	6.0	229	1.2	6.0	0.3	24	3.20
933177	Drill Core	6.19	55.9	5912	9.5	38	1.8	3.7	11.8	499	4.90	21.0	2.4	463.5	3.5	128	0.2	2.4	0.3	29	1.74
933178	Drill Core	6.59	87.4	5317	10.2	50	1.6	2.5	11.5	539	5.18	9.3	4.8	367.4	12.1	322	0.3	4.9	0.2	33	2.46
933179	Drill Core	6.19	40.8	8259	7.2	38	2.5	3.2	13.8	321	6.29	51.7	1.3	584.0	7.9	133	0.2	9.9	0.3	39	1.05
933180	Rock Pulp	0.09	7.6	3071	15.1	128	0.6	146.9	14.3	826	5.96	12.8	0.2	263.4	1.5	174	0.6	8.7	0.5	57	2.85
933181	Drill Core	8.05	55.2	7968	6.3	39	2.4	3.3	13.2	322	5.93	4.0	2.6	560.6	10.0	687	0.1	2.1	0.3	48	1.25
933182	Drill Core	6.75	115.2	5410	7.8	43	1.7	3.2	12.5	444	7.05	13.3	2.3	420.9	9.9	148	0.3	5.7	0.2	35	1.62
933183	Drill Core	6.37	21.0	7518	15.0	63	3.4	3.2	12.6	1014	7.84	12.6	1.3	529.3	5.9	106	0.3	13.7	0.4	27	1.67
933184	Drill Core	6.73	19.2	8960	14.3	55	4.4	3.6	13.0	955	8.10	6.7	1.3	625.5	6.5	63	0.3	4.8	0.5	29	1.09
933185	Drill Core	7.03	43.6	6460	8.5	55	2.7	3.3	16.0	560	8.22	146.5	1.2	463.5	6.4	72	0.3	53.5	0.3	34	1.27
933186	Drill Core	6.97	19.1	9643	11.5	50	3.2	4.6	17.3	432	8.95	73.0	0.9	842.5	5.6	56	0.2	19.0	0.4	38	0.67
933187	Drill Core	7.53	27.0	8708	10.2	43	3.0	3.9	14.1	452	8.70	128.0	1.0	730.0	6.3	51	0.2	4.2	0.4	42	0.73
933188	Drill Core	8.48	16.8	>10000	9.7	51	4.8	4.9	17.0	396	9.10	19.1	0.8	1093	5.3	69	0.3	9.5	0.7	59	0.83
933189	Drill Core	6.26	42.6	9767	20.8	98	4.2	4.5	18.0	633	8.38	34.8	0.9	854.7	5.5	69	0.6	6.7	0.6	40	1.23
933190	Drill Core	7.01	64.2	>10000	18.0	82	3.9	4.6	17.5	762	8.23	13.6	1.4	740.2	7.3	67	0.4	20.6	0.7	43	1.30
933191	Drill Core	7.31	78.4	6031	9.2	45	2.3	3.0	19.7	473	6.43	6.8	1.9	472.6	12.0	175	0.2	3.2	0.3	40	1.35
933192	Drill Core	8.59	163.0	7957	12.0	63	3.1	3.6	19.4	726	7.67	6.9	1.6	576.7	9.2	108	0.3	4.6	0.4	47	1.23
933193	Drill Core	6.43	23.4	7843	9.0	51	2.6	3.2	13.7	577	8.79	4.7	1.4	646.3	9.0	72	0.2	5.7	0.4	66	1.28
933194	Drill Core	6.86	22.8	4867	8.4	47	1.9	3.0	11.0	592	6.04	11.6	2.0	317.6	10.9	116	0.1	43.5	0.3	41	1.40
933195	Drill Core	6.35	82.2	5128	8.8	45	1.2	2.9	11.5	500	6.26	19.8	1.9	353.5	10.6	88	0.1	47.5	0.3	33	1.27
933196	Drill Core	8.28	24.2	5891	11.2	59	1.8	2.7	14.0	574	7.23	31.2	1.7	419.7	9.6	58	0.3	52.2	0.3	34	1.06
933197	Drill Core	7.10	6.8	5316	7.9	54	2.1	2.8	12.2	490	7.34	41.2	1.6	369.3	10.7	49	0.2	58.2	0.3	40	1.09
933198	Drill Core	6.85	22.7	3278	9.1	52	1.1	3.0	11.7	649	5.52	39.9	2.8	242.1	12.4	85	0.2	50.7	0.2	36	1.97

This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**

110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo

Report Date: November 06, 2008

Page: 2 of 3 Part 2

CERTIFICATE OF ANALYSIS

SMI08000981.2

Method	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	7AR
Analyte	P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se	Cu	
Unit	%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	%	
MDL	0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5	0.001	
933169	Drill Core	0.107	10	4	0.82	168	<0.001	3	0.36	0.007	0.27	0.6	0.14	3.6	0.3	0.93	<1	1.6	N.A.
933170	Drill Core	0.123	19	3	0.58	107	<0.001	4	0.40	0.010	0.29	0.1	0.29	3.2	0.3	1.03	1	1.3	N.A.
933171	Drill Core	0.089	9	5	0.62	138	<0.001	3	0.34	0.004	0.27	0.6	0.23	2.6	0.3	0.95	1	2.0	N.A.
933172	Drill Core	0.107	11	5	0.58	126	<0.001	4	0.34	0.010	0.29	0.1	0.37	2.8	0.2	0.98	1	1.8	N.A.
933173	Drill Core	0.104	11	8	0.61	93	0.002	2	0.45	0.019	0.28	0.4	0.25	3.1	0.2	1.01	2	2.2	N.A.
933174	Drill Core	0.152	14	6	1.21	196	0.056	2	1.06	0.036	0.47	<0.1	0.64	8.0	0.4	0.71	5	2.9	N.A.
933175	Drill Core	0.097	8	11	0.90	317	0.045	3	0.75	0.029	0.49	0.4	0.25	7.7	0.4	0.51	3	1.2	N.A.
933176	Drill Core	0.106	7	5	0.93	113	0.002	3	0.36	0.008	0.30	<0.1	0.36	4.3	0.2	1.36	1	4.9	N.A.
933177	Drill Core	0.035	4	7	0.48	96	<0.001	3	0.29	0.010	0.29	0.2	0.38	4.1	0.3	0.91	1	3.5	N.A.
933178	Drill Core	0.115	16	6	0.63	210	0.001	3	0.34	0.010	0.26	0.1	0.40	3.8	0.2	0.78	2	2.6	N.A.
933179	Drill Core	0.059	5	12	0.41	109	<0.001	3	0.29	0.009	0.22	0.2	0.35	2.0	0.1	1.15	2	4.5	N.A.
933180	Rock Pulp	0.110	6	179	1.14	38	0.002	6	1.16	0.053	0.37	0.4	1.32	6.8	0.2	2.84	3	9.2	N.A.
933181	Drill Core	0.090	9	7	0.47	97	0.003	2	0.34	0.015	0.22	0.1	0.54	2.5	0.1	1.19	3	4.9	N.A.
933182	Drill Core	0.095	9	9	0.53	141	<0.001	4	0.36	0.013	0.29	0.1	0.36	3.0	0.1	0.85	2	3.1	N.A.
933183	Drill Core	0.041	3	8	0.72	108	<0.001	3	0.22	0.004	0.22	<0.1	0.29	1.6	0.2	1.18	1	4.6	N.A.
933184	Drill Core	0.041	3	15	0.46	90	<0.001	4	0.23	0.005	0.23	0.2	0.33	1.7	0.1	1.38	2	5.5	N.A.
933185	Drill Core	0.047	4	10	0.43	119	<0.001	3	0.21	0.005	0.21	0.1	0.52	1.8	0.1	1.18	2	3.6	N.A.
933186	Drill Core	0.035	3	19	0.33	84	<0.001	2	0.19	0.008	0.20	0.6	0.61	1.7	<0.1	1.18	2	7.3	N.A.
933187	Drill Core	0.035	3	10	0.37	87	<0.001	3	0.21	0.005	0.18	0.3	0.56	1.4	0.2	1.45	2	4.7	N.A.
933188	Drill Core	0.024	3	18	0.39	38	<0.001	3	0.19	0.007	0.17	0.3	0.57	1.2	0.1	1.70	3	9.1	1.579
933189	Drill Core	0.029	3	10	0.45	45	<0.001	3	0.20	0.005	0.20	0.2	0.48	1.3	0.2	2.07	2	7.2	N.A.
933190	Drill Core	0.038	5	12	0.48	63	0.001	2	0.20	0.005	0.22	<0.1	0.47	1.6	0.2	1.73	1	7.3	1.127
933191	Drill Core	0.091	10	11	0.42	101	0.001	3	0.28	0.013	0.23	<0.1	0.22	2.5	0.1	1.09	2	5.2	N.A.
933192	Drill Core	0.047	7	10	0.36	83	0.001	2	0.21	0.008	0.22	0.2	0.24	1.7	0.1	1.68	2	6.3	N.A.
933193	Drill Core	0.053	6	11	0.41	120	0.001	3	0.29	0.009	0.21	0.2	0.28	2.0	0.1	1.02	3	4.4	N.A.
933194	Drill Core	0.080	11	7	0.44	204	0.002	3	0.30	0.011	0.25	0.1	0.18	2.4	0.2	0.66	2	3.2	N.A.
933195	Drill Core	0.073	10	11	0.40	209	<0.001	5	0.30	0.012	0.27	<0.1	0.18	2.5	0.1	0.64	2	3.4	N.A.
933196	Drill Core	0.062	6	9	0.38	125	<0.001	3	0.27	0.007	0.25	0.2	0.41	1.9	0.2	1.05	2	4.9	N.A.
933197	Drill Core	0.064	5	12	0.39	123	<0.001	4	0.25	0.008	0.23	0.1	0.32	2.1	0.1	0.83	2	4.2	N.A.
933198	Drill Core	0.116	14	7	0.61	256	0.001	4	0.24	0.011	0.22	<0.1	0.45	3.5	0.1	0.50	1	2.6	N.A.

This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**

110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo

Report Date: November 06, 2008

Page: 3 of 3 Part 1

CERTIFICATE OF ANALYSIS

SMI08000981.2

Method	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
Unit	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	
MDL	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	
933199	Drill Core	6.52	3.7	1352	8.4	55	0.4	3.2	10.7	742	5.18	30.0	3.6	109.3	13.3	146	0.2	41.4	0.2	62	2.97
933200	Drill Core	6.67	3.2	1491	10.5	35	0.6	2.1	8.3	428	3.36	86.1	4.2	94.6	15.5	107	0.2	49.2	0.2	20	2.16
933201	Drill Core	7.26	4.4	1093	7.4	33	0.5	2.1	7.1	495	3.51	47.8	3.7	88.1	14.8	155	0.1	11.8	0.1	22	2.47
933202	Drill Core	5.57	1.4	669.5	6.0	30	0.3	2.0	5.7	434	3.34	10.4	3.2	54.1	14.9	741	0.1	14.0	0.1	21	2.61
933203	Drill Core	7.12	2.4	975.7	9.2	36	0.4	2.3	6.4	704	3.86	25.3	3.4	59.2	14.5	163	0.1	4.9	0.1	28	2.48
933204	Drill Core	6.81	4.6	934.3	10.0	42	0.3	2.5	6.9	700	3.33	11.2	4.4	81.9	14.6	603	0.1	1.6	0.1	36	2.43
933205	Drill Core	6.68	4.7	483.0	16.7	54	0.3	2.1	6.1	1013	2.34	39.1	8.0	36.8	17.0	276	0.2	2.5	0.5	20	3.09
933206	Drill Core	7.24	3.5	793.0	9.6	33	0.2	1.9	6.8	535	2.37	14.3	5.8	44.2	18.3	915	0.1	0.9	0.1	23	2.60
933207	Drill Core	6.17	1473	>10000	14.3	65	4.5	5.7	18.0	578	4.40	167.5	5.0	817.4	16.2	338	0.6	1.7	0.5	29	4.42
933208	Drill Core	6.95	2.9	650.4	6.2	24	0.2	1.6	5.3	401	2.01	3.4	5.8	36.2	18.7	792	0.1	0.2	<0.1	28	2.52
933209	Drill Core	6.64	10.8	2216	8.4	38	0.6	2.4	9.0	517	3.61	8.1	3.8	156.4	14.3	698	0.2	0.5	0.2	34	3.13
933210	Rock Pulp	0.09	7.6	3150	15.1	130	0.6	117.8	13.9	829	5.50	12.0	0.2	263.3	1.5	180	0.6	8.2	0.4	52	2.82
933211	Drill Core	5.79	6.2	2552	11.9	36	0.7	2.4	8.6	500	3.85	230.9	3.5	237.8	12.0	260	0.1	9.7	0.2	18	4.15
933212	Drill Core	6.15	29.2	1807	18.3	44	0.6	2.8	7.7	438	2.52	319.7	5.1	144.0	13.2	177	0.2	3.7	0.2	8	4.51
933213	Drill Core	6.35	26.3	1415	32.6	99	0.5	1.8	6.3	409	2.26	81.8	6.5	113.6	14.9	2877	0.5	3.1	0.3	14	2.92
933214	Drill Core	6.65	5.6	1979	7.4	23	0.7	2.7	7.8	265	2.34	107.2	6.2	128.9	13.4	1274	0.1	3.7	0.1	13	2.73
933215	Drill Core	5.68	8.1	1511	6.7	17	0.5	2.0	6.2	227	1.94	15.4	6.3	95.4	14.0	4226	<0.1	4.1	0.1	13	2.58
933216	Drill Core	6.87	47.9	742.8	7.4	18	0.3	2.0	7.8	264	2.40	33.1	6.4	35.3	13.1	2382	<0.1	1.5	<0.1	16	3.22
933217	Drill Core	6.71	28.7	2036	16.6	48	0.7	6.8	12.3	479	3.76	33.3	0.9	96.3	1.5	249	0.3	3.5	0.2	16	3.82
933218	Drill Core	6.27	26.3	1881	12.7	41	0.7	6.8	10.7	394	3.21	245.7	2.5	125.9	7.0	120	<0.1	104.9	0.2	17	2.42
933219	Drill Core	6.87	40.5	2826	15.1	60	0.9	22.2	11.2	522	3.30	29.8	3.6	192.3	9.4	101	0.3	4.0	0.3	18	2.94
933220	Drill Core	7.64	10.8	1170	9.3	19	0.4	2.6	6.5	339	2.54	40.6	5.1	68.9	14.4	159	0.1	20.7	0.1	10	2.84
933221	Drill Core	5.76	14.5	1026	10.1	24	0.4	2.2	9.0	405	2.45	21.4	5.7	56.0	13.1	872	<0.1	15.2	0.1	21	3.25
933222	Drill Core	5.20	43.5	1097	10.7	35	0.4	6.2	10.1	471	2.21	5.0	2.7	49.5	5.4	370	0.2	1.2	0.2	30	2.20
933223	Drill Core	7.69	66.5	2300	12.4	49	0.8	10.8	16.5	587	4.06	4.7	0.6	153.0	1.2	429	0.3	0.7	0.2	47	2.25
933224	Drill Core	7.00	43.4	603.1	17.9	58	0.3	7.8	7.5	600	2.07	8.7	0.7	55.8	1.5	92	0.2	0.3	0.2	39	1.56



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
 Report Date: November 06, 2008

Page: 3 of 3 Part 2

CERTIFICATE OF ANALYSIS

SMI08000981.2

Method	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	7AR
Analyte	P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se	Cu	
Unit	%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	%	
MDL	0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5	0.001	
933199	Drill Core	0.139	19	5	0.81	326	0.001	5	0.30	0.015	0.24	<0.1	0.91	5.2	0.1	0.37	2	1.1	N.A.
933200	Drill Core	0.124	13	4	0.50	151	<0.001	6	0.29	0.009	0.24	<0.1	1.41	3.4	0.1	0.87	<1	1.4	N.A.
933201	Drill Core	0.124	13	5	0.49	477	<0.001	8	0.31	0.014	0.28	<0.1	0.48	3.5	0.1	0.31	<1	0.8	N.A.
933202	Drill Core	0.120	14	5	0.53	607	0.003	6	0.31	0.021	0.28	<0.1	0.10	3.6	0.1	0.22	<1	0.9	N.A.
933203	Drill Core	0.105	13	6	0.60	394	<0.001	4	0.32	0.019	0.26	<0.1	0.12	3.1	0.1	0.33	<1	1.0	N.A.
933204	Drill Core	0.125	24	5	0.55	427	0.002	4	0.37	0.044	0.27	0.1	1.26	4.3	0.1	0.35	2	1.0	N.A.
933205	Drill Core	0.122	26	4	0.67	340	<0.001	7	0.37	0.042	0.26	1.4	0.88	3.9	0.2	0.46	<1	0.9	N.A.
933206	Drill Core	0.124	24	5	0.56	376	0.003	5	0.35	0.040	0.25	<0.1	1.35	3.9	0.1	0.39	1	1.1	N.A.
933207	Drill Core	0.234	51	3	0.88	68	0.004	5	0.31	0.023	0.25	0.2	2.07	3.7	0.6	2.20	1	9.5	1.435
933208	Drill Core	0.124	27	4	0.42	637	0.004	3	0.31	0.036	0.21	<0.1	0.21	3.9	<0.1	0.23	1	0.7	N.A.
933209	Drill Core	0.135	18	4	0.54	321	0.002	3	0.30	0.029	0.24	<0.1	0.35	3.5	0.1	0.58	1	1.6	N.A.
933210	Rock Pulp	0.121	5	147	1.12	53	0.002	5	1.01	0.055	0.35	0.4	1.27	6.5	0.2	2.92	2	8.5	N.A.
933211	Drill Core	0.127	13	<1	0.51	215	<0.001	5	0.31	0.022	0.27	<0.1	0.52	3.0	0.2	0.75	<1	2.2	N.A.
933212	Drill Core	0.121	9	2	0.39	289	0.001	7	0.36	0.018	0.31	0.1	0.84	2.4	0.2	0.64	<1	1.7	N.A.
933213	Drill Core	0.119	12	3	0.53	376	0.001	6	0.39	0.024	0.30	0.4	1.03	2.9	0.2	0.60	1	1.5	N.A.
933214	Drill Core	0.120	10	3	0.42	304	<0.001	6	0.37	0.026	0.27	<0.1	0.31	2.7	0.2	0.52	<1	1.9	N.A.
933215	Drill Core	0.128	15	3	0.45	410	0.002	6	0.37	0.028	0.28	<0.1	0.31	2.6	0.2	0.64	1	1.5	N.A.
933216	Drill Core	0.138	20	3	0.52	252	0.004	3	0.42	0.034	0.27	0.2	0.25	3.4	0.2	0.82	1	1.0	N.A.
933217	Drill Core	0.084	6	3	0.88	212	0.001	3	0.32	0.033	0.25	<0.1	0.40	6.0	0.2	0.90	1	2.3	N.A.
933218	Drill Core	0.092	8	3	0.63	298	0.001	5	0.40	0.034	0.29	0.1	0.14	5.1	0.2	0.65	1	1.7	N.A.
933219	Drill Core	0.082	8	8	0.65	260	0.002	5	0.36	0.036	0.28	<0.1	0.38	4.0	0.2	0.74	<1	2.2	N.A.
933220	Drill Core	0.135	16	2	0.62	217	0.001	4	0.40	0.039	0.32	<0.1	0.23	2.9	0.2	0.81	<1	1.4	N.A.
933221	Drill Core	0.142	29	2	0.59	293	0.003	4	0.62	0.049	0.27	<0.1	0.15	2.9	0.2	0.59	2	1.1	N.A.
933222	Drill Core	0.075	17	8	0.56	277	0.004	3	0.71	0.049	0.25	<0.1	0.18	4.4	0.2	0.75	3	1.3	N.A.
933223	Drill Core	0.067	9	12	0.68	253	0.008	2	0.98	0.050	0.28	<0.1	0.18	5.1	0.2	0.81	4	1.7	N.A.
933224	Drill Core	0.064	8	13	0.64	322	0.003	2	1.19	0.060	0.30	<0.1	0.18	5.4	0.3	0.41	5	0.8	N.A.

QUALITY CONTROL REPORT

SMI08000981.2

Method	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
Unit	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	
MDL	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	
Pulp Duplicates																					
933193	Drill Core	6.43	23.4	7843	9.0	51	2.6	3.2	13.7	577	8.79	4.7	1.4	646.3	9.0	72	0.2	5.7	0.4	66	1.28
REP 933193	QC		21.0	7633	8.8	54	2.6	3.1	13.0	569	8.55	5.0	1.4	635.8	8.8	72	0.1	5.4	0.4	64	1.25
933220	Drill Core	7.64	10.8	1170	9.3	19	0.4	2.6	6.5	339	2.54	40.6	5.1	68.9	14.4	159	0.1	20.7	0.1	10	2.84
REP 933220	QC		11.2	1180	9.1	21	0.4	2.3	6.9	351	2.58	41.2	4.9	66.1	13.6	159	0.1	20.2	0.1	9	2.87
Core Reject Duplicates																					
933195	Drill Core	6.35	82.2	5128	8.8	45	1.2	2.9	11.5	500	6.26	19.8	1.9	353.5	10.6	88	0.1	47.5	0.3	33	1.27
DUP 933195	QC		93.2	5266	9.3	46	1.3	3.0	12.0	542	6.40	20.7	1.9	380.8	10.9	87	0.1	49.8	0.3	32	1.28
Reference Materials																					
STD DS7	Standard		21.2	106.5	73.4	415	0.9	56.7	9.6	641	2.39	52.1	5.3	83.0	4.9	78	6.3	6.3	5.0	86	1.00
STD DS7	Standard		21.0	110.1	71.4	402	0.8	58.3	9.5	632	2.47	52.7	5.3	66.2	4.4	79	6.2	6.3	4.8	84	1.00
STD DS7	Standard		21.0	104.2	72.8	397	0.9	55.5	9.6	602	2.33	54.5	5.3	73.2	4.6	70	6.8	6.2	4.9	78	0.94
STD DS7	Standard		20.8	107.1	68.0	409	0.8	56.0	9.7	640	2.35	54.2	4.9	63.2	4.3	78	6.7	5.9	4.8	78	0.97
STD R4A	Standard																				
STD SF-3A	Standard																				
STD DS7 Expected			20.9	109	70.6	411	0.9	56	9.7	627	2.39	48.2	4.9	70	4.4	69	6.4	5.9	4.5	86	0.93
STD R4A Expected																					
STD SF-3A Expected																					
BLK	Blank		<0.1	1.3	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01
BLK	Blank		<0.1	0.5	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01
BLK	Blank																				
Prep Wash																					
G1	Prep Blank	<0.01	0.6	6.2	2.4	49	<0.1	4.6	4.6	572	2.11	<0.5	1.7	<0.5	3.8	61	<0.1	<0.1	0.2	43	0.54
G1	Prep Blank	<0.01	0.4	3.5	2.6	51	<0.1	4.1	4.6	575	1.99	<0.5	1.7	<0.5	4.0	58	<0.1	<0.1	0.1	40	0.54

QUALITY CONTROL REPORT

SMI08000981.2

Method		1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	7AR
Analyte		P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se	Cu
Unit		%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	%
MDL		0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5	0.001
Pulp Duplicates																			
933193	Drill Core	0.053	6	11	0.41	120	0.001	3	0.29	0.009	0.21	0.2	0.28	2.0	0.1	1.02	3	4.4	N.A.
REP 933193	QC	0.054	6	10	0.40	114	0.001	3	0.28	0.008	0.20	0.2	0.28	1.8	0.1	0.97	3	4.2	
933220	Drill Core	0.135	16	2	0.62	217	0.001	4	0.40	0.039	0.32	<0.1	0.23	2.9	0.2	0.81	<1	1.4	N.A.
REP 933220	QC	0.132	15	2	0.62	201	0.001	4	0.36	0.038	0.31	<0.1	0.23	3.1	0.2	0.82	<1	1.4	
Core Reject Duplicates																			
933195	Drill Core	0.073	10	11	0.40	209	<0.001	5	0.30	0.012	0.27	<0.1	0.18	2.5	0.1	0.64	2	3.4	N.A.
DUP 933195	QC	0.070	10	10	0.41	199	0.001	4	0.31	0.013	0.28	0.1	0.17	2.3	0.1	0.66	2	3.7	N.A.
Reference Materials																			
STD DS7	Standard	0.079	14	178	1.06	385	0.119	41	1.05	0.090	0.46	3.6	0.22	2.7	4.2	0.20	5	3.5	
STD DS7	Standard	0.080	13	173	1.05	374	0.110	41	1.01	0.087	0.44	4.3	0.23	2.6	4.5	0.20	5	4.4	
STD DS7	Standard	0.084	12	164	1.03	410	0.114	43	1.00	0.086	0.42	4.1	0.21	2.3	4.4	0.19	5	3.5	
STD DS7	Standard	0.085	13	168	1.03	398	0.116	40	1.01	0.087	0.44	4.3	0.18	2.3	4.2	0.19	5	3.9	
STD R4A	Standard																		0.505
STD SF-3A	Standard																		0.770
STD DS7 Expected		0.08	13	163	1.05	370	0.124	39	0.959	0.073	0.44	3.8	0.2	2.5	4.2	0.21	4.6	3.5	
STD R4A Expected																			0.502
STD SF-3A Expected																			0.7705
BLK	Blank	<0.001	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5	
BLK	Blank	<0.001	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5	
BLK	Blank																		<0.001
Prep Wash																			
G1	Prep Blank	0.083	8	14	0.62	250	0.124	1	0.99	0.071	0.60	0.4	<0.01	2.7	0.4	<0.05	5	<0.5	N.A.
G1	Prep Blank	0.082	7	11	0.61	248	0.122	<1	0.96	0.060	0.60	0.2	<0.01	2.4	0.4	<0.05	5	<0.5	N.A.



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.

Vancouver BC V6C 1Z7 Canada

Submitted By:

Glen Garratt

Receiving Lab:

Canada-Smithers

Received:

September 29, 2008

Report Date:

October 17, 2008

Page:

1 of 3

CERTIFICATE OF ANALYSIS

SMI08000982.1

CLIENT JOB INFORMATION

Project: Zymo
Shipment ID: zy-co-08-07
P.O. Number
Number of Samples: 31

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
DISP-RJT Dispose of Reject After 90 days

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Mincord Exploration Consultants Ltd.
110 - 325 Howe St.
Vancouver BC V6C 1Z7
Canada

CC: Bob Johnston

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status
R150	30	Crush split and pulverize drill core to 200 mesh		
1DX15	31	1:1:1 Aqua Regia digestion ICP-MS analysis	15	Completed

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only. All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.

“**” asterisk indicates that an analytical result could not be provided due to unusually high levels of interference from other elements.



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**

110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo

Report Date: October 17, 2008

Page: 2 of 3 Part 1

CERTIFICATE OF ANALYSIS

SMI08000982.1

Method	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
Unit	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	
MDL	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	
933267	Drill Core	6.52	23.0	3624	12.5	48	1.3	4.8	11.3	483	3.19	16.4	0.4	212.0	1.4	104	0.2	2.4	0.3	20	2.15
933268	Drill Core	7.07	64.3	6449	17.9	52	1.8	5.2	15.0	560	4.08	56.3	1.6	451.3	2.4	83	0.3	2.3	0.9	22	2.02
933269	Drill Core	8.68	16.3	4921	15.6	36	1.8	3.7	12.8	536	4.58	23.5	0.7	343.5	0.8	56	0.2	3.3	0.3	13	1.73
933270	Rock Pulp	0.09	7.3	3006	13.4	124	0.5	119.1	13.4	745	5.41	12.4	0.2	249.8	1.4	180	0.5	7.4	0.4	50	2.66
933271	Drill Core	7.82	17.9	7879	17.4	38	3.3	5.0	15.6	684	5.59	61.8	0.5	581.4	1.3	79	0.3	3.5	0.4	18	2.88
933272	Drill Core	7.48	8.1	6880	15.6	58	2.8	3.7	18.4	669	7.66	42.2	0.7	566.7	3.1	65	0.2	9.0	0.4	27	2.41
933273	Drill Core	7.87	3.1	4281	12.9	75	1.5	4.4	18.7	617	5.84	24.2	0.9	397.0	4.5	103	0.4	16.7	0.2	39	2.69
933274	Drill Core	8.00	7.6	4711	14.7	64	2.1	3.7	14.2	583	4.21	63.3	2.4	486.8	7.0	110	0.2	119.1	0.5	24	3.15
933275	Drill Core	6.97	1.7	2205	9.0	49	0.9	3.0	11.9	479	4.02	13.2	4.3	186.1	12.9	107	0.1	7.4	0.2	38	2.22
933276	Drill Core	7.96	4.1	2085	8.5	47	0.7	2.9	12.0	531	4.32	12.0	2.8	185.3	9.7	565	0.1	7.6	0.1	50	2.47
933277	Drill Core	7.82	9.6	1839	12.9	57	1.3	3.3	7.5	438	2.76	139.7	2.5	113.2	7.3	210	0.2	339.0	0.2	32	2.49
933278	Drill Core	7.63	8.0	3618	20.6	52	1.6	7.6	11.6	504	3.59	84.9	0.3	241.0	1.0	75	0.2	161.0	0.2	39	1.35
933279	Drill Core	7.81	6.9	3500	12.4	45	1.2	11.6	14.9	592	4.66	65.0	0.8	258.0	1.1	111	0.3	40.1	0.3	56	2.16
933280	Drill Core	7.38	16.3	5010	20.1	41	2.4	8.9	16.1	1215	5.08	12.0	1.8	431.1	4.8	148	0.2	8.1	0.4	48	2.86
933281	Drill Core	6.46	20.8	3630	13.3	31	1.5	11.9	10.1	521	2.68	13.2	1.7	212.1	6.4	82	0.2	17.9	0.3	10	2.35
933282	Drill Core	7.32	3.3	2726	12.1	33	1.2	8.3	9.1	388	3.20	12.3	5.4	256.3	16.2	79	0.1	4.8	0.3	23	2.23
933283	Drill Core	7.53	2.8	2134	10.3	61	0.8	7.7	11.4	459	3.38	16.9	2.1	136.0	7.1	98	0.2	12.3	0.2	27	2.16
933284	Drill Core	7.13	38.1	3937	22.3	67	1.8	8.2	13.1	754	3.37	37.7	2.5	326.9	2.3	111	0.3	37.9	0.4	25	3.75
933285	Drill Core	7.53	3.4	783.9	14.4	52	0.4	4.3	9.5	896	2.93	4.6	3.2	56.6	5.5	828	0.1	1.1	0.2	46	3.17
933286	Drill Core	7.30	3.2	36.7	5.5	56	<0.1	1.9	8.4	857	2.73	3.1	4.3	9.1	8.1	588	<0.1	1.1	0.1	55	2.99
933287	Drill Core	6.57	4.8	79.8	16.9	98	0.1	2.6	9.4	892	2.85	13.7	4.5	9.1	7.9	231	<0.1	13.2	0.3	39	3.05
933288	Drill Core	7.48	6.2	2292	18.8	86	1.1	8.8	12.4	781	2.92	14.2	3.0	129.8	4.7	94	0.2	9.4	0.3	33	2.57
933289	Drill Core	7.13	10.1	3092	24.3	51	1.4	14.1	15.7	769	3.54	10.9	1.5	188.8	2.1	462	0.2	10.2	0.4	37	2.78
933290	Drill Core	7.57	6.3	2429	17.4	47	1.0	6.4	7.8	520	2.46	7.6	1.6	130.4	7.4	155	<0.1	2.5	0.3	20	1.92
933291	Drill Core	7.17	6.3	3014	17.3	43	1.3	6.6	12.4	561	3.42	22.1	2.5	172.0	10.1	138	0.2	26.5	0.3	25	2.15
933292	Drill Core	7.57	19.1	4087	30.0	62	2.0	10.0	15.6	926	3.33	15.3	0.7	213.9	1.5	127	0.3	25.8	0.5	19	2.74
933293	Drill Core	7.57	10.0	3093	17.3	69	1.4	6.7	14.5	898	3.63	34.0	2.3	197.9	8.8	365	0.2	50.0	0.3	32	2.69
933294	Drill Core	7.26	5.0	2329	29.1	85	1.1	8.8	18.3	1011	5.31	3.4	1.7	137.8	6.4	387	0.2	1.8	0.3	109	2.42
933295	Drill Core	7.83	11.4	4064	22.1	81	1.5	12.1	25.9	841	4.78	6.2	1.7	254.8	6.4	213	0.2	1.7	0.4	82	3.55
933296	Drill Core	7.78	16.3	3799	22.6	99	1.2	8.7	17.9	605	4.29	7.6	1.2	230.0	5.5	198	0.5	9.6	0.2	75	2.41



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
Report Date: October 17, 2008

Page: 2 of 3 **Part** 2

CERTIFICATE OF ANALYSIS

SMI08000982.1

Method Analyte Unit MDL	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
	P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Ti	S	Ga	Se	
	%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
	0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.01	0.01	0.1	0.01	0.05	1	0.5	
933267	Drill Core	0.070	3	3	0.63	216	0.001	2	0.34	0.027	0.25	1.2	0.24	5.2	0.2	0.66	1	2.8
933268	Drill Core	0.115	8	3	0.60	112	<0.001	4	0.39	0.013	0.30	3.9	0.43	4.3	0.3	1.18	1	4.5
933269	Drill Core	0.042	2	3	0.54	95	<0.001	3	0.29	0.008	0.30	0.7	0.23	4.8	0.3	0.93	<1	3.5
933270	Rock Pulp	0.115	5	147	1.06	39	0.001	5	1.05	0.052	0.33	0.4	1.19	5.8	0.2	2.86	3	8.0
933271	Drill Core	0.046	2	4	0.98	46	<0.001	3	0.30	0.008	0.25	2.2	0.32	4.1	0.3	2.25	1	5.1
933272	Drill Core	0.075	4	4	0.86	94	<0.001	3	0.30	0.008	0.29	0.4	0.28	3.6	0.3	1.65	1	5.6
933273	Drill Core	0.159	10	3	0.96	199	<0.001	3	0.52	0.010	0.32	0.9	0.25	4.5	0.2	0.83	2	4.2
933274	Drill Core	0.136	13	2	0.85	96	<0.001	3	0.36	0.007	0.30	0.3	0.37	3.2	0.2	1.20	1	4.1
933275	Drill Core	0.124	17	4	0.77	175	0.001	3	0.57	0.021	0.28	0.5	0.32	2.7	0.2	0.78	3	2.4
933276	Drill Core	0.151	17	2	0.97	277	0.004	3	0.71	0.021	0.28	0.2	0.27	4.2	0.2	0.63	4	2.1
933277	Drill Core	0.081	11	4	0.48	277	<0.001	3	0.44	0.006	0.25	0.7	0.39	3.2	0.2	0.44	2	1.3
933278	Drill Core	0.075	5	9	0.39	156	<0.001	2	0.41	0.005	0.29	0.3	0.37	3.3	0.2	0.90	1	2.8
933279	Drill Core	0.073	6	14	0.41	166	<0.001	2	0.40	0.019	0.31	0.2	0.15	4.4	0.2	0.97	2	2.7
933280	Drill Core	0.122	8	12	0.53	79	<0.001	3	0.50	0.017	0.32	0.2	0.19	4.0	0.3	1.73	2	4.0
933281	Drill Core	0.065	4	7	0.59	70	<0.001	2	0.30	0.007	0.24	0.4	0.31	2.0	0.2	1.35	<1	2.9
933282	Drill Core	0.117	14	3	0.57	146	<0.001	2	0.34	0.008	0.25	0.1	0.26	2.4	0.1	0.90	1	2.5
933283	Drill Core	0.085	11	4	0.70	178	<0.001	3	0.38	0.012	0.26	0.1	0.31	3.4	0.2	0.79	1	2.3
933284	Drill Core	0.082	21	6	0.69	149	<0.001	3	0.56	0.014	0.29	<0.1	0.20	3.6	0.2	1.11	1	4.1
933285	Drill Core	0.141	28	7	0.82	716	0.002	2	0.97	0.033	0.24	<0.1	0.06	3.1	0.2	0.24	3	1.1
933286	Drill Core	0.158	40	3	0.80	319	0.002	1	0.58	0.040	0.18	<0.1	0.04	3.6	<0.1	0.05	3	<0.5
933287	Drill Core	0.167	39	1	0.73	720	<0.001	3	0.53	0.021	0.26	0.1	0.32	3.2	0.1	0.13	2	<0.5
933288	Drill Core	0.131	22	5	0.47	179	0.001	2	0.54	0.015	0.28	0.1	0.20	2.6	0.2	0.73	2	2.0
933289	Drill Core	0.107	11	20	0.34	115	0.002	2	0.45	0.032	0.26	0.5	0.10	2.7	0.1	1.17	2	2.7
933290	Drill Core	0.050	10	4	0.42	131	0.001	2	0.52	0.036	0.29	0.1	0.18	2.4	0.1	0.76	2	2.1
933291	Drill Core	0.069	11	5	0.55	121	0.001	2	0.44	0.028	0.25	0.2	0.20	2.7	0.1	1.02	2	2.9
933292	Drill Core	0.239	12	5	0.55	67	0.002	2	0.60	0.027	0.32	1.1	0.14	3.8	0.2	1.52	2	2.7
933293	Drill Core	0.099	15	5	0.86	121	0.005	2	0.76	0.038	0.34	0.2	0.22	3.8	0.2	0.96	3	1.8
933294	Drill Core	0.175	22	10	1.62	135	0.043	2	1.90	0.068	0.23	0.3	0.18	7.6	0.1	0.77	8	1.3
933295	Drill Core	0.179	25	10	1.61	143	0.011	2	1.98	0.040	0.22	0.1	0.16	5.8	0.2	1.26	8	3.3
933296	Drill Core	0.140	16	9	1.40	190	0.029	3	1.62	0.051	0.31	0.1	0.24	6.1	0.2	0.77	7	2.9



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.

Vancouver BC V6C 1Z7 Canada

Project:

Zymo

Report Date:

October 17, 2008

Page:

3 of 3

Part 1

CERTIFICATE OF ANALYSIS

SMI08000982.1

Method	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
Unit	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	
MDL	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	
933297	Drill Core	7.31	21.8	2122	20.5	44	0.9	5.2	12.0	799	2.36	52.7	0.4	123.5	1.6	79	0.2	80.7	0.3	10	1.82



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.

Vancouver BC V6C 1Z7 Canada

Project:

Zymo

Report Date:

October 17, 2008

Page:

3 of 3

Part 2

CERTIFICATE OF ANALYSIS

SMI08000982.1

Method	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se	
Unit	%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
MDL	0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5	
933297	Drill Core	0.030	5	2	0.48	154	<0.001	2	0.53	0.034	0.42	0.2	0.15	3.0	0.3	0.87	1	2.0

QUALITY CONTROL REPORT

SMI08000982.1

Method	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
Unit	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	
MDL	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	
Core Reject Duplicates																					
933268	Drill Core	7.07	64.3	6449	17.9	52	1.8	5.2	15.0	560	4.08	56.3	1.6	451.3	2.4	83	0.3	2.3	0.9	22	2.02
DUP 933268	QC		70.0	6520	18.1	55	1.9	5.1	15.8	575	4.30	58.3	2.0	497.1	2.4	73	0.4	2.4	0.4	22	1.98
Reference Materials																					
STD DS7	Standard		20.2	107.5	69.5	406	0.8	52.3	9.4	609	2.30	52.6	4.8	66.0	4.3	71	6.6	6.0	4.3	78	0.92
STD DS7	Standard		19.8	106.8	74.0	391	0.9	53.3	8.6	583	2.30	51.6	5.2	91.6	4.6	70	6.7	6.4	4.5	79	0.93
STD DS7	Standard		20.0	109.9	78.4	410	1.0	60.5	9.5	636	2.35	53.9	5.4	69.2	5.0	81	6.3	6.6	5.4	76	0.94
STD DS7	Standard		21.2	109.2	84.2	416	0.9	57.6	9.5	634	2.42	51.8	6.2	82.4	5.6	84	6.0	6.9	5.4	80	1.00
STD DS7 Expected			20.9	109	70.6	411	0.9	56	9.7	627	2.39	48.2	4.9	70	4.4	69	6.4	5.9	4.5	86	0.93
BLK	Blank		<0.1	0.8	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01
BLK	Blank		<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01
Prep Wash																					
G1	Prep Blank	<0.01	2.8	2.8	2.8	46	<0.1	4.4	4.6	557	2.02	<0.5	1.9	<0.5	4.4	59	<0.1	<0.1	0.1	40	0.56
G1	Prep Blank	<0.01	0.7	3.2	2.4	44	<0.1	3.5	4.5	549	1.76	<0.5	1.7	<0.5	3.6	60	<0.1	<0.1	<0.1	37	0.56

QUALITY CONTROL REPORT

SMI08000982.1

Method		1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte		P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
Unit		%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm
MDL		0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5
Core Reject Duplicates																		
933268	Drill Core	0.115	8	3	0.60	112	<0.001	4	0.39	0.013	0.30	3.9	0.43	4.3	0.3	1.18	1	4.5
DUP 933268	QC	0.111	8	3	0.59	126	0.001	3	0.38	0.014	0.29	2.8	0.48	4.5	0.2	1.22	1	4.5
Reference Materials																		
STD DS7	Standard	0.079	12	169	0.99	375	0.111	38	0.95	0.080	0.43	4.1	0.22	2.2	4.1	0.19	5	3.4
STD DS7	Standard	0.082	13	162	0.98	395	0.109	41	0.95	0.081	0.42	4.1	0.21	2.1	4.3	0.19	5	3.6
STD DS7	Standard	0.078	13	175	1.03	385	0.120	41	0.99	0.084	0.43	4.4	0.21	2.3	4.7	0.18	5	3.4
STD DS7	Standard	0.075	15	179	1.06	393	0.130	38	1.04	0.089	0.43	4.1	0.21	2.5	4.6	0.19	5	3.1
STD DS7 Expected		0.08	13	163	1.05	370	0.124	39	0.959	0.073	0.44	3.8	0.2	2.5	4.2	0.21	4.6	3.5
BLK	Blank	<0.001	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
BLK	Blank	<0.001	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
Prep Wash																		
G1	Prep Blank	0.088	8	11	0.62	257	0.141	<1	1.02	0.077	0.57	2.1	<0.01	2.0	0.4	<0.05	5	<0.5
G1	Prep Blank	0.085	7	9	0.60	237	0.137	<1	0.98	0.071	0.55	1.0	<0.01	1.8	0.3	<0.05	5	<0.5



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.

Vancouver BC V6C 1Z7 Canada

Submitted By:

Glen Garratt

Receiving Lab:

Canada-Smithers

Received:

September 29, 2008

Report Date:

October 29, 2008

Page:

1 of 3

CERTIFICATE OF ANALYSIS

SMI08000986.1

CLIENT JOB INFORMATION

Project: Zymo
Shipment ID: zy-co-08-06
P.O. Number
Number of Samples: 42

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
DISP-RJT Dispose of Reject After 90 days

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Mincord Exploration Consultants Ltd.
110 - 325 Howe St.
Vancouver BC V6C 1Z7
Canada

CC: Bob Johnston

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status
R150	41	Crush split and pulverize drill core to 200 mesh		
1DX15	42	1:1:1 Aqua Regia digestion ICP-MS analysis	15	Completed

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only. All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.

“**” asterisk indicates that an analytical result could not be provided due to unusually high levels of interference from other elements.



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
 Report Date: October 29, 2008

Page: 2 of 3 Part 1

CERTIFICATE OF ANALYSIS

SMI08000986.1

Method	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
Unit	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	
MDL	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	
933225	Drill Core	7.08	35.0	511.4	20.5	54	0.3	8.0	7.3	510	1.91	9.3	1.5	40.5	3.3	213	0.3	0.6	0.4	33	2.35
933226	Drill Core	7.27	35.5	658.6	5.3	27	0.3	2.5	11.1	324	3.35	3.2	7.3	47.5	15.4	335	<0.1	0.2	0.1	88	2.97
933227	Drill Core	7.37	31.4	1189	6.7	32	0.6	6.9	14.9	375	3.78	5.2	7.7	73.0	14.1	246	0.1	0.3	0.2	80	3.01
933228	Drill Core	6.93	30.9	838.3	10.0	42	0.4	6.5	10.8	389	2.65	1.8	2.1	62.0	4.7	171	0.2	0.3	0.2	60	2.73
933229	Drill Core	6.04	41.2	723.5	20.1	60	0.3	3.6	9.2	457	2.26	1.8	1.2	53.3	4.0	224	0.4	0.6	0.2	25	1.51
933230	Drill Core	6.83	51.7	645.5	13.2	37	0.3	3.1	5.4	447	1.48	1.4	0.7	51.0	1.6	578	0.1	0.5	0.2	30	1.94
933231	Drill Core	6.11	60.9	1083	14.4	44	0.5	5.6	9.8	348	1.92	2.7	1.8	71.0	4.0	304	0.2	1.8	0.2	37	1.74
933232	Drill Core	7.35	24.0	1884	10.3	57	0.9	9.5	30.0	429	4.82	8.2	1.4	144.2	6.1	125	0.2	0.8	0.3	95	2.57
933233	Drill Core	7.38	36.4	1631	12.2	60	0.8	9.7	26.4	516	4.35	2.8	2.1	132.0	6.7	122	0.3	0.6	0.3	99	2.61
933234	Drill Core	7.33	33.8	1298	17.6	54	0.6	9.8	21.5	594	3.78	7.4	1.1	105.2	3.9	222	0.2	0.8	0.3	56	3.72
933235	Drill Core	6.88	56.6	256.6	10.1	29	0.1	6.9	8.4	497	1.90	11.0	0.3	19.8	1.3	68	0.1	1.2	0.2	17	2.47
933236	Drill Core	7.78	34.3	1121	19.1	52	0.5	10.0	18.6	522	3.80	89.2	0.5	56.2	1.6	56	0.2	1.5	0.3	32	2.37
933237	Drill Core	7.94	41.2	1132	21.9	52	0.5	12.1	14.5	508	2.63	114.7	0.4	54.6	1.6	89	0.2	1.0	0.3	26	2.50
933238	Drill Core	7.19	167.2	750.0	18.0	31	0.3	5.8	7.8	397	1.54	9.7	0.7	41.6	1.5	80	0.2	0.5	0.2	13	2.26
933239	Drill Core	7.89	37.1	1733	11.8	62	0.7	8.5	22.8	422	4.23	9.1	1.2	106.0	4.6	208	0.2	0.3	0.3	94	2.69
933240	Rock Pulp	0.09	7.6	3203	17.0	138	0.6	117.4	14.8	885	5.87	12.5	0.3	231.5	1.7	190	0.5	8.4	0.5	51	2.80
933241	Drill Core	7.61	25.0	964.2	10.0	54	0.5	7.9	28.4	406	4.63	4.4	1.3	60.0	5.3	132	0.1	0.2	0.3	90	2.70
933242	Drill Core	6.54	150.3	1087	21.8	37	0.6	9.5	13.8	351	2.47	3.0	0.8	79.2	2.7	112	0.3	0.4	0.3	50	2.44
933243	Drill Core	5.51	55.0	409.0	28.5	35	0.4	9.0	10.4	335	2.28	5.1	0.5	35.6	1.7	94	0.2	0.4	0.2	39	2.40
933244	Drill Core	6.58	27.7	345.8	15.4	36	0.2	9.2	9.0	339	1.85	1.1	0.4	22.6	1.7	64	<0.1	0.6	0.2	41	2.57
933245	Drill Core	6.96	35.3	1769	16.0	61	1.0	9.2	34.8	451	5.24	4.4	1.3	85.4	5.1	68	0.3	3.1	0.6	72	3.30
933246	Drill Core	7.38	43.2	1472	13.0	59	0.8	7.6	27.4	404	4.99	1.5	1.6	71.2	5.4	153	0.3	1.5	0.4	107	2.18
933247	Drill Core	7.20	32.6	1260	8.5	54	0.6	8.4	22.9	405	5.01	0.9	2.1	77.3	6.4	122	<0.1	0.8	0.4	119	1.97
933248	Drill Core	7.22	44.1	1299	10.2	51	0.7	9.2	26.3	396	5.58	1.1	1.8	87.9	6.5	97	0.1	1.0	0.3	114	2.64
933249	Drill Core	5.92	37.1	673.6	7.7	51	0.4	7.3	19.7	412	5.08	1.6	1.7	58.2	6.5	158	0.1	0.6	0.2	112	2.28
933250	Drill Core	7.27	57.2	1564	8.1	48	0.8	9.4	23.6	383	5.03	1.4	1.3	107.5	4.6	70	0.2	0.9	0.3	126	1.88
933251	Drill Core	7.12	31.6	1160	7.1	52	0.5	6.9	20.0	365	4.99	1.8	1.0	73.7	4.3	75	0.1	0.2	0.2	131	1.83
933252	Drill Core	7.75	89.8	1573	10.3	49	0.7	8.4	28.9	337	4.69	3.3	0.8	76.9	2.7	650	0.2	1.2	0.3	95	2.44
933253	Drill Core	7.61	56.1	1055	13.1	48	0.4	10.4	21.3	390	3.63	2.4	0.8	55.3	2.7	573	0.2	0.9	0.2	78	2.77
933254	Drill Core	7.47	54.9	1259	11.2	44	0.5	8.4	25.8	364	4.06	4.5	1.0	66.6	3.6	163	0.2	1.9	0.3	51	4.29



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
Report Date: October 29, 2008

Page: 2 of 3 **Part** 2

CERTIFICATE OF ANALYSIS

SMI08000986.1

Method	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se	
Unit	%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
MDL	0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5	
933225	Drill Core	0.084	12	10	0.49	208	0.003	3	1.08	0.058	0.33	0.2	0.48	4.5	0.4	0.68	4	0.7
933226	Drill Core	0.170	38	5	0.94	93	0.034	2	1.34	0.065	0.24	1.6	0.29	3.6	0.2	1.43	6	1.0
933227	Drill Core	0.137	29	9	0.88	82	0.049	3	1.43	0.058	0.20	<0.1	0.23	4.3	0.1	1.56	7	1.2
933228	Drill Core	0.099	11	7	0.98	187	0.037	4	1.54	0.065	0.49	0.1	0.15	5.4	0.4	0.83	6	1.0
933229	Drill Core	0.025	13	6	0.87	345	0.005	2	1.39	0.069	0.25	<0.1	0.16	2.4	0.2	0.48	5	0.8
933230	Drill Core	0.016	11	7	0.52	548	0.003	3	1.08	0.055	0.28	<0.1	0.11	3.5	0.2	0.29	3	<0.5
933231	Drill Core	0.044	14	9	0.78	260	0.017	2	1.23	0.078	0.24	0.1	0.30	3.3	0.2	0.55	5	1.1
933232	Drill Core	0.172	15	6	1.62	78	0.088	2	2.25	0.102	0.29	0.1	0.25	6.1	0.3	1.44	10	2.8
933233	Drill Core	0.168	14	6	1.55	86	0.114	2	2.46	0.142	0.45	0.1	0.20	7.3	0.5	1.30	10	2.5
933234	Drill Core	0.126	10	7	1.06	122	0.027	4	1.98	0.074	0.47	<0.1	0.13	5.8	0.5	1.18	7	1.7
933235	Drill Core	0.022	2	3	0.28	154	0.003	3	1.22	0.038	0.57	<0.1	0.19	3.6	0.7	0.97	2	<0.5
933236	Drill Core	0.041	5	8	0.52	43	0.002	3	1.58	0.046	0.40	<0.1	0.15	5.2	0.5	1.74	4	1.4
933237	Drill Core	0.065	6	6	0.47	114	0.002	3	1.29	0.057	0.43	<0.1	0.27	4.9	0.4	1.31	3	1.7
933238	Drill Core	0.036	8	3	0.28	191	0.001	3	0.91	0.060	0.43	<0.1	0.21	3.5	0.4	0.78	2	0.8
933239	Drill Core	0.153	14	7	1.46	123	0.107	3	2.38	0.150	0.38	<0.1	0.18	8.1	0.4	1.37	9	2.6
933240	Rock Pulp	0.118	6	177	1.17	37	0.005	5	1.14	0.055	0.35	0.4	1.37	6.6	0.2	2.90	3	9.0
933241	Drill Core	0.165	15	6	1.58	83	0.119	1	2.26	0.118	0.28	0.3	0.09	7.0	0.3	1.87	9	3.4
933242	Drill Core	0.064	10	9	0.88	128	0.013	2	1.65	0.069	0.42	0.3	0.10	4.9	0.4	1.20	5	1.8
933243	Drill Core	0.045	7	9	0.65	123	0.002	2	1.39	0.046	0.39	0.6	0.05	4.1	0.4	1.11	4	0.9
933244	Drill Core	0.052	9	10	0.71	333	0.004	2	1.50	0.045	0.40	0.2	0.07	4.7	0.4	0.49	5	0.6
933245	Drill Core	0.130	17	7	1.36	26	0.008	2	2.12	0.053	0.17	0.2	0.19	5.3	0.2	2.57	10	4.6
933246	Drill Core	0.129	11	9	1.46	57	0.148	<1	2.32	0.111	0.33	0.1	0.20	8.0	0.5	2.08	10	3.3
933247	Drill Core	0.176	13	7	1.79	48	0.203	2	2.45	0.126	0.36	0.1	0.11	8.8	0.5	1.71	9	2.5
933248	Drill Core	0.175	14	6	1.69	36	0.198	2	2.33	0.109	0.24	0.2	0.15	8.4	0.3	1.74	9	2.4
933249	Drill Core	0.168	14	6	1.76	115	0.176	2	2.44	0.117	0.30	0.3	0.07	8.2	0.4	1.25	9	1.5
933250	Drill Core	0.166	11	10	1.77	38	0.206	2	2.07	0.092	0.19	0.3	0.08	9.2	0.3	2.09	9	3.6
933251	Drill Core	0.166	9	9	1.80	36	0.250	2	2.21	0.108	0.21	0.2	0.07	9.9	0.3	1.81	9	2.4
933252	Drill Core	0.163	11	10	1.62	53	0.135	2	2.08	0.114	0.19	0.1	0.08	6.8	0.2	2.67	8	4.8
933253	Drill Core	0.153	13	8	1.46	99	0.024	1	2.06	0.084	0.19	<0.1	0.03	5.3	0.2	1.49	7	3.1
933254	Drill Core	0.150	14	5	1.13	81	0.019	2	1.94	0.068	0.30	<0.1	0.03	5.8	0.3	1.79	5	3.6

This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.



AcmeLabs ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
Report Date: October 29, 2008

Page: 3 of 3 **Part** 1

CERTIFICATE OF ANALYSIS

SMI08000986.1

	Method Analyte Unit MDL	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
		kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%
		0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01
933255	Drill Core	9.34	26.7	587.5	12.6	35	0.3	9.0	17.0	416	2.69	22.3	0.6	41.4	2.0	131	0.1	7.3	0.2	18	3.43	
933256	Drill Core	4.93	28.5	2105	13.0	39	1.3	3.0	26.3	458	3.38	26.6	9.0	111.9	13.4	105	0.2	8.5	0.4	10	2.85	
933257	Drill Core	6.39	23.1	1716	9.7	38	0.8	2.8	24.9	368	3.44	20.8	7.2	76.5	14.9	124	0.3	6.3	0.2	9	2.82	
933258	Drill Core	7.03	24.0	959.7	9.4	20	0.4	1.6	16.3	421	2.28	23.8	8.7	36.2	12.4	304	0.1	4.0	0.2	18	3.08	
933259	Drill Core	6.24	55.3	3358	8.9	19	1.4	2.2	18.4	299	2.62	8.6	8.7	173.8	13.4	207	0.1	3.5	0.3	10	2.85	
933260	Drill Core	6.75	20.6	1894	7.4	22	0.8	2.8	12.7	351	3.00	7.2	4.0	112.0	11.9	458	0.1	3.5	0.1	19	2.26	
933261	Drill Core	6.63	38.0	4850	11.3	26	2.3	3.9	12.7	401	3.16	12.1	4.5	314.4	8.9	633	0.2	3.3	0.3	18	2.64	
933262	Drill Core	5.82	22.2	4122	12.2	48	1.6	4.4	14.7	327	4.02	3.5	4.2	251.3	10.2	919	0.3	2.0	0.2	47	2.12	
933263	Drill Core	7.74	18.8	6470	16.2	44	2.6	4.9	15.5	372	3.65	7.9	2.3	375.4	6.5	440	0.3	5.9	0.3	22	3.01	
933264	Drill Core	7.59	22.4	3276	15.8	42	1.0	4.5	10.7	599	2.71	7.3	1.2	184.3	2.2	118	0.2	1.5	0.2	14	2.50	
933265	Drill Core	6.82	32.3	3505	9.8	54	1.3	7.5	10.9	618	4.06	3.3	0.6	296.0	1.1	83	0.2	3.7	0.2	44	1.39	
933266	Drill Core	6.70	23.1	2957	8.8	50	1.1	6.2	11.0	576	3.76	4.7	0.4	221.7	1.0	63	0.2	3.8	0.2	29	1.36	



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
Report Date: October 29, 2008

Page: 3 of 3 **Part** 2

CERTIFICATE OF ANALYSIS

SMI08000986.1

Method	Analyte	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
		P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
Unit		%	ppm	ppm	%	ppm	%	ppm	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
MDL		0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.05	1	0.5	
933255	Drill Core	0.085	5	3	0.64	129	0.002	2	0.82	0.048	0.36	<0.1	0.03	3.8	0.3	1.04	2	1.7
933256	Drill Core	0.112	11	6	0.54	48	0.001	2	0.35	0.011	0.28	<0.1	0.22	2.5	0.2	1.99	<1	3.6
933257	Drill Core	0.109	11	2	0.56	42	0.001	3	0.35	0.013	0.27	<0.1	0.18	3.2	0.2	2.13	<1	7.2
933258	Drill Core	0.108	17	3	0.65	79	0.001	2	0.35	0.010	0.23	<0.1	0.23	3.0	0.1	1.10	<1	3.2
933259	Drill Core	0.103	18	2	0.57	57	0.001	2	0.31	0.014	0.22	<0.1	0.23	2.7	0.1	1.47	<1	5.2
933260	Drill Core	0.107	13	4	0.63	119	0.002	2	0.36	0.017	0.24	<0.1	0.21	2.8	0.1	0.91	1	2.4
933261	Drill Core	0.096	8	9	0.63	85	0.001	2	0.37	0.013	0.24	<0.1	0.19	2.4	0.1	1.31	1	3.5
933262	Drill Core	0.138	22	5	0.89	121	0.009	2	0.82	0.025	0.23	<0.1	0.28	3.5	0.1	0.98	4	2.9
933263	Drill Core	0.145	9	7	0.83	124	0.004	2	0.55	0.017	0.33	<0.1	0.37	4.2	0.2	1.08	1	4.1
933264	Drill Core	0.065	3	2	0.72	183	<0.001	2	0.30	0.014	0.24	<0.1	0.36	6.2	0.2	0.71	<1	2.5
933265	Drill Core	0.053	5	14	0.69	189	0.008	3	0.47	0.042	0.30	<0.1	0.20	6.8	0.2	0.59	2	2.6
933266	Drill Core	0.050	4	8	0.63	199	0.003	3	0.42	0.034	0.29	<0.1	0.24	7.8	0.2	0.47	2	1.7

QUALITY CONTROL REPORT

SMI08000986.1

Method	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
Unit	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	
MDL	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	
Pulp Duplicates																					
933231	Drill Core	6.11	60.9	1083	14.4	44	0.5	5.6	9.8	348	1.92	2.7	1.8	71.0	4.0	304	0.2	1.8	0.2	37	1.74
REP 933231	QC		62.6	1087	13.7	43	0.5	5.8	10.0	333	1.91	2.5	1.9	91.9	3.8	282	0.2	1.7	0.2	38	1.74
REP 933251	QC		30.0	1198	7.6	52	0.5	7.0	20.1	363	5.14	1.9	1.0	88.8	4.5	78	0.2	0.2	0.3	136	1.90
Core Reject Duplicates																					
933251	Drill Core	7.12	31.6	1160	7.1	52	0.5	6.9	20.0	365	4.99	1.8	1.0	73.7	4.3	75	0.1	0.2	0.2	131	1.83
DUP 933251	QC		30.6	1103	6.7	50	0.5	6.3	18.8	363	4.79	2.2	1.0	59.1	4.2	74	0.2	0.1	0.2	130	1.77
Reference Materials																					
STD DS7	Standard		20.0	109.9	78.4	410	1.0	60.5	9.5	636	2.35	53.9	5.4	69.2	5.0	81	6.3	6.6	5.4	76	0.94
STD DS7	Standard		21.2	109.2	84.2	416	0.9	57.6	9.5	634	2.42	51.8	6.2	82.4	5.6	84	6.0	6.9	5.4	80	1.00
STD DS7	Standard		21.4	118.9	66.9	383	0.8	59.5	10.4	614	2.35	49.6	4.6	84.7	4.1	67	6.1	5.8	4.2	78	0.94
STD DS7	Standard		22.0	114.4	66.1	387	0.8	56.7	10.0	622	2.36	47.7	4.6	80.3	4.2	69	6.1	5.7	4.2	81	0.97
STD DS7	Standard		20.0	106.8	61.8	400	0.8	55.0	9.0	621	2.41	48.2	4.4	62.2	3.9	65	5.8	5.0	4.0	85	0.97
STD DS7	Standard		21.1	105.8	60.0	396	0.9	56.6	9.1	621	2.39	49.8	4.1	70.9	3.8	68	5.2	4.8	3.9	81	0.99
STD DS7 Expected			20.9	109	70.6	411	0.9	56	9.7	627	2.39	48.2	4.9	70	4.4	69	6.4	5.9	4.5	86	0.93
BLK	Blank		<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01
BLK	Blank		<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	0.12
BLK	Blank		<0.1	0.9	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01
Prep Wash																					
G1	Prep Blank	<0.01	0.2	22.3	204.1	504	2.7	4.7	4.5	689	2.08	7.3	2.3	17.1	4.7	60	2.6	4.3	0.1	37	0.52
G1	Prep Blank	<0.01	0.2	26.9	245.4	532	3.2	4.3	4.6	726	2.06	8.1	1.9	10.2	4.4	54	2.9	5.6	<0.1	36	0.51

QUALITY CONTROL REPORT

SMI08000986.1

Method		1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte		P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
Unit		%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm
MDL		0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5
Pulp Duplicates																		
933231	Drill Core	0.044	14	9	0.78	260	0.017	2	1.23	0.078	0.24	0.1	0.30	3.3	0.2	0.55	5	1.1
REP 933231	QC	0.043	13	8	0.78	279	0.017	2	1.29	0.085	0.24	0.1	0.28	3.3	0.2	0.55	5	1.5
REP 933251	QC	0.177	9	7	1.86	36	0.265	2	2.25	0.111	0.21	0.2	0.07	10.4	0.3	1.86	9	2.9
Core Reject Duplicates																		
933251	Drill Core	0.166	9	9	1.80	36	0.250	2	2.21	0.108	0.21	0.2	0.07	9.9	0.3	1.81	9	2.4
DUP 933251	QC	0.173	9	9	1.85	36	0.256	3	2.29	0.118	0.22	0.2	0.07	10.3	0.3	1.63	9	2.5
Reference Materials																		
STD DS7	Standard	0.078	13	175	1.03	385	0.120	41	0.99	0.084	0.43	4.4	0.21	2.3	4.7	0.18	5	3.4
STD DS7	Standard	0.075	15	179	1.06	393	0.130	38	1.04	0.089	0.43	4.1	0.21	2.5	4.6	0.19	5	3.1
STD DS7	Standard	0.073	11	187	1.02	352	0.130	37	0.97	0.080	0.41	3.8	0.18	2.5	3.5	0.19	4	3.3
STD DS7	Standard	0.076	12	187	1.01	350	0.132	39	1.00	0.082	0.41	3.8	0.18	2.7	3.8	0.20	4	3.7
STD DS7	Standard	0.075	12	186	1.00	360	0.113	41	0.97	0.083	0.42	4.1	0.18	2.5	4.1	0.19	5	3.9
STD DS7	Standard	0.071	13	192	1.01	356	0.119	39	0.99	0.084	0.42	4.2	0.18	2.6	3.8	0.19	5	3.4
STD DS7 Expected		0.08	13	163	1.05	370	0.124	39	0.959	0.073	0.44	3.8	0.2	2.5	4.2	0.21	4.6	3.5
BLK	Blank	<0.001	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
BLK	Blank	<0.001	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
BLK	Blank	<0.001	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
Prep Wash																		
G1	Prep Blank	0.089	8	9	0.60	240	0.139	<1	0.95	0.059	0.55	<0.1	0.02	1.9	0.4	0.13	5	<0.5
G1	Prep Blank	0.084	8	9	0.61	261	0.137	1	0.95	0.054	0.52	0.1	0.02	2.0	0.4	0.13	5	<0.5



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.

Vancouver BC V6C 1Z7 Canada

Submitted By:

Glen Garratt

Receiving Lab:

Canada-Smithers

Received:

September 29, 2008

Report Date:

October 29, 2008

Page:

1 of 3

CERTIFICATE OF ANALYSIS

SMI08000987.1

CLIENT JOB INFORMATION

Project: Zymo
Shipment ID: zy-co-08-08
P.O. Number
Number of Samples: 48

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
DISP-RJT Dispose of Reject After 90 days

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Mincord Exploration Consultants Ltd.
110 - 325 Howe St.
Vancouver BC V6C 1Z7
Canada

CC: Bob Johnston

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status
R150	46	Crush split and pulverize drill core to 200 mesh		
1DX15	48	1:1:1 Aqua Regia digestion ICP-MS analysis	15	Completed

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only. All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.

** asterisk indicates that an analytical result could not be provided due to unusually high levels of interference from other elements.



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**

110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo

Report Date: October 29, 2008

Page: 2 of 3 Part 1

CERTIFICATE OF ANALYSIS

SMI08000987.1

Method	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
Unit	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	
MDL	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	
933298	Drill Core	7.57	24.6	3136	14.5	70	1.2	6.1	14.1	780	2.99	90.6	0.6	115.3	1.2	104	0.2	222.1	0.2	23	2.81
933299	Drill Core	7.08	9.1	3376	9.6	53	1.1	5.9	15.2	607	4.08	6.3	1.3	197.3	4.2	284	<0.1	1.6	0.2	48	2.54
933300	Rock Pulp	0.09	7.6	3129	12.4	121	0.5	134.4	14.7	800	5.75	11.9	0.2	193.7	1.3	168	0.5	7.9	0.4	52	2.78
933301	Drill Core	6.42	14.6	2050	7.2	30	0.7	3.9	10.1	457	3.22	3.6	4.1	99.0	13.1	653	<0.1	1.8	0.1	39	2.55
933302	Drill Core	7.20	17.8	1923	10.3	35	0.7	3.8	12.2	507	4.13	3.5	2.8	120.1	13.4	399	0.1	3.2	0.2	45	2.17
933303	Drill Core	7.38	36.5	2001	16.1	97	0.9	3.1	17.6	859	4.05	24.9	3.4	124.2	12.0	410	0.7	2.6	0.3	25	3.91
933304	Drill Core	7.22	19.7	1945	7.4	30	0.6	3.4	12.0	426	2.57	1.6	2.2	79.9	6.7	351	0.1	1.0	0.2	34	1.78
933305	Drill Core	7.25	11.1	3445	12.0	51	1.2	3.7	18.5	435	4.39	3.1	0.8	187.0	2.9	216	0.3	0.9	0.3	46	1.68
933306	Drill Core	8.22	14.1	2098	6.6	57	0.8	1.9	18.9	381	4.83	1.7	0.8	102.5	3.1	103	0.2	0.7	0.2	69	1.97
933307	Drill Core	7.56	67.6	3009	7.8	57	1.0	2.7	20.0	462	4.66	3.0	1.0	151.4	3.7	86	0.2	0.7	0.3	64	2.22
933308	Drill Core	6.46	15.7	2494	18.0	53	1.1	2.6	16.7	1359	4.06	4.8	1.1	136.3	3.1	98	0.2	0.7	0.3	55	2.57
933309	Drill Core	4.86	23.6	2311	10.8	37	1.1	5.8	19.5	1070	3.51	3.3	3.5	141.5	6.3	562	0.1	0.6	0.3	49	3.63
933310	Drill Core	7.68	32.2	2352	9.2	40	1.0	5.6	21.7	467	4.21	3.6	3.4	136.9	7.3	547	0.1	0.9	0.4	49	2.38
933311	Drill Core	7.24	133.2	1655	11.0	31	0.7	4.9	11.3	677	2.78	3.1	2.4	79.5	1.7	152	<0.1	1.1	0.3	21	1.99
933312	Drill Core	5.33	103.6	1921	5.7	23	0.7	4.0	10.9	648	2.74	1.9	3.6	89.8	2.4	585	<0.1	1.1	0.2	15	1.74
933313	Drill Core	7.13	89.6	1227	11.2	39	0.6	4.8	11.6	697	3.02	2.0	0.8	79.3	0.8	43	<0.1	0.7	0.3	18	1.57
933314	Drill Core	7.01	45.7	1928	11.7	45	0.8	7.0	16.0	627	3.11	2.2	1.3	100.8	1.4	44	0.2	1.3	0.4	28	1.01
933315	Drill Core	7.63	66.0	1357	12.7	30	0.7	6.8	13.1	567	2.23	4.7	1.9	72.1	1.8	122	0.1	3.3	0.4	17	1.79
933316	Drill Core	6.11	96.6	2110	68.1	163	1.3	8.3	21.6	508	2.71	15.2	1.1	109.0	0.6	42	1.6	3.0	0.6	21	1.22
933317	Drill Core	5.91	71.7	1832	85.5	212	1.2	8.5	20.0	342	2.80	13.8	0.6	84.7	1.0	39	1.8	1.5	0.5	19	0.95
933318	Drill Core	6.63	97.9	1549	62.9	261	0.9	6.6	14.9	286	1.98	12.2	0.7	79.9	1.2	49	2.6	2.1	0.4	12	1.23
933319	Drill Core	6.78	134.4	1936	15.5	47	0.6	3.3	11.3	343	2.57	1.6	2.8	99.8	9.6	438	0.4	0.9	0.2	42	2.53
933320	Drill Core	6.58	42.3	1221	13.3	37	0.5	4.2	10.3	317	2.07	4.0	1.9	72.7	5.4	527	0.1	0.9	0.3	34	1.79
933321	Drill Core	7.21	23.9	2213	8.4	67	0.7	10.0	30.4	491	5.29	5.6	1.3	138.8	5.7	930	0.2	0.9	0.2	111	3.22
933322	Drill Core	6.85	56.4	1260	20.4	31	0.5	6.0	16.0	283	2.34	54.1	0.9	56.9	2.2	249	0.2	21.4	0.3	24	1.77
933323	Drill Core	6.66	57.0	450.4	8.0	15	0.2	6.4	11.5	257	1.31	45.8	0.3	25.1	0.8	55	0.2	0.9	0.2	6	1.38
933324	Drill Core	6.91	17.4	633.0	20.9	75	0.2	7.0	26.5	566	3.98	205.7	0.9	26.3	3.0	121	0.5	2.9	0.5	51	3.44
933325	Drill Core	6.76	10.4	393.5	14.8	41	0.1	6.5	21.0	344	3.94	5.3	1.1	17.7	3.3	174	0.2	1.5	0.2	73	3.14
933326	Drill Core	7.48	9.0	493.1	9.9	38	0.1	6.9	22.4	288	4.64	<0.5	0.9	15.0	4.3	441	<0.1	0.5	0.2	95	2.42
933327	Drill Core	7.57	17.6	522.3	8.5	36	0.1	6.7	20.8	298	4.22	<0.5	0.8	14.9	4.2	608	<0.1	0.4	0.1	90	2.33

This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
Report Date: October 29, 2008

Page: 2 of 3 **Part** 2

CERTIFICATE OF ANALYSIS

SMI08000987.1

Method Analyte Unit MDL	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
	P %	La ppm	Cr ppm	Mg %	Ba ppm	Ti %	B ppm	Al %	Na %	K %	W ppm	Hg ppm	Sc ppm	Tl ppm	S %	Ga ppm	Se ppm	
933298	Drill Core	0.033	5	3	0.48	123	<0.001	2	0.56	0.019	0.25	0.1	0.19	4.4	0.2	0.95	2	2.7
933299	Drill Core	0.098	11	8	0.85	116	0.007	2	1.08	0.037	0.28	<0.1	0.13	3.9	0.2	0.89	4	2.4
933300	Rock Pulp	0.107	5	185	1.11	41	0.002	5	1.08	0.050	0.33	0.4	1.04	6.5	0.1	2.88	2	8.1
933301	Drill Core	0.111	21	3	0.61	179	0.002	2	0.66	0.028	0.21	<0.1	0.13	2.5	<0.1	0.71	3	1.6
933302	Drill Core	0.110	14	8	0.62	145	0.002	2	0.71	0.025	0.22	<0.1	0.17	2.6	<0.1	0.80	4	1.5
933303	Drill Core	0.111	14	4	0.68	31	0.001	2	0.65	0.029	0.20	<0.1	0.69	2.2	0.2	3.02	2	3.8
933304	Drill Core	0.069	14	9	0.43	71	0.002	1	0.84	0.034	0.35	<0.1	0.08	2.2	0.2	1.18	4	1.6
933305	Drill Core	0.113	13	7	0.74	47	0.004	6	1.30	0.045	0.29	<0.1	0.07	2.6	0.2	1.60	6	3.1
933306	Drill Core	0.153	14	8	1.01	73	0.063	2	1.55	0.068	0.16	0.3	0.06	3.4	<0.1	1.48	8	2.7
933307	Drill Core	0.153	16	2	1.03	75	0.050	1	1.64	0.066	0.16	<0.1	0.16	3.5	0.2	1.52	7	2.1
933308	Drill Core	0.125	12	5	0.96	107	0.042	2	1.40	0.054	0.28	<0.1	0.11	3.2	0.3	1.39	6	2.7
933309	Drill Core	0.107	16	5	0.58	63	0.005	2	1.13	0.030	0.32	<0.1	0.04	3.9	0.2	1.66	3	2.7
933310	Drill Core	0.102	17	7	0.64	69	0.003	2	1.23	0.045	0.31	<0.1	0.05	4.3	0.2	1.48	5	2.4
933311	Drill Core	0.034	6	6	0.36	35	0.001	1	0.65	0.043	0.38	<0.1	0.39	2.8	0.3	1.34	2	1.7
933312	Drill Core	0.031	8	6	0.33	68	0.002	2	0.59	0.046	0.41	<0.1	0.10	2.7	0.3	1.13	2	1.6
933313	Drill Core	0.012	3	6	0.42	94	0.003	2	1.04	0.048	0.39	0.1	0.10	2.7	0.3	0.97	3	1.2
933314	Drill Core	0.009	4	5	0.40	71	0.004	2	1.39	0.064	0.42	<0.1	0.12	3.2	0.4	1.10	4	1.8
933315	Drill Core	0.012	5	3	0.28	84	0.001	2	0.78	0.056	0.36	<0.1	0.30	2.8	0.3	1.06	2	2.1
933316	Drill Core	0.017	5	3	0.27	45	<0.001	2	0.90	0.063	0.37	<0.1	0.14	3.2	0.3	1.58	3	2.6
933317	Drill Core	0.010	4	3	0.22	64	<0.001	2	0.98	0.066	0.37	<0.1	0.15	1.9	0.3	1.71	3	2.5
933318	Drill Core	0.010	3	1	0.16	91	<0.001	1	0.74	0.067	0.36	<0.1	0.22	1.4	0.2	1.20	3	2.2
933319	Drill Core	0.106	38	4	0.65	198	0.002	2	1.14	0.060	0.23	<0.1	0.10	2.3	0.2	0.77	5	1.7
933320	Drill Core	0.060	14	4	0.44	148	0.002	2	1.04	0.070	0.31	<0.1	0.08	2.2	0.2	0.79	4	1.2
933321	Drill Core	0.196	22	8	1.87	138	0.067	3	2.40	0.124	0.54	0.2	0.10	10.0	0.5	1.26	9	3.5
933322	Drill Core	0.064	5	3	0.68	149	0.005	2	1.01	0.082	0.40	<0.1	0.07	4.7	0.3	1.09	3	1.6
933323	Drill Core	0.035	3	1	0.20	54	<0.001	1	0.60	0.131	0.24	<0.1	0.06	4.2	0.2	1.06	<1	2.3
933324	Drill Core	0.104	9	4	1.16	39	0.007	2	1.40	0.094	0.28	<0.1	1.64	6.9	0.3	2.66	4	4.5
933325	Drill Core	0.122	13	7	1.29	78	0.015	2	2.11	0.106	0.31	<0.1	0.14	6.1	0.4	1.86	7	2.3
933326	Drill Core	0.145	12	8	1.73	50	0.089	2	2.47	0.156	0.15	<0.1	0.09	5.9	0.2	2.17	8	2.6
933327	Drill Core	0.153	12	8	1.74	57	0.056	2	2.59	0.207	0.19	<0.1	0.07	5.3	0.3	1.99	8	3.0

This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
 Report Date: October 29, 2008

Page: 3 of 3 Part 1

CERTIFICATE OF ANALYSIS

SMI08000987.1

Method	Analyte	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca
Unit		kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%
MDL		0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01
933328	Drill Core	6.65	11.9	575.3	15.4	41	0.2	3.9	19.3	282	4.04	<0.5	2.0	17.7	7.7	196	0.2	0.7	0.2	54	3.23
933329	Drill Core	8.43	20.2	405.7	14.8	51	0.1	2.5	9.2	241	2.70	<0.5	3.4	20.7	10.3	445	0.3	0.3	0.2	43	1.86
933330	Rock Pulp	0.09	7.4	3309	16.5	140	0.6	141.0	14.1	823	5.95	11.1	0.2	220.3	1.7	189	0.6	8.6	0.5	56	2.81
933331	Drill Core	6.62	13.5	484.8	16.1	49	0.2	2.8	15.3	234	3.58	2.8	3.7	36.2	10.2	487	0.3	1.1	0.2	37	2.95
933332	Drill Core	7.37	31.5	422.9	28.2	39	0.2	1.9	15.5	285	2.79	5.1	3.4	44.2	9.4	381	0.4	3.5	0.2	21	6.09
933333	Drill Core	7.93	16.4	466.4	23.2	37	0.2	2.7	19.7	245	3.58	2.2	3.6	24.8	9.6	392	0.2	1.1	0.2	24	4.32
933334	Drill Core	7.23	54.2	546.3	22.7	39	0.2	5.9	23.9	275	3.80	3.8	1.7	43.6	4.5	471	0.3	3.0	0.2	32	4.06
933335	Drill Core	7.74	50.9	486.6	14.4	38	0.2	5.1	20.9	331	3.51	1.0	0.8	29.6	0.7	1712	0.2	1.4	0.2	49	3.43
933336	Drill Core	6.72	16.6	262.1	18.5	37	0.2	9.1	19.6	371	3.46	5.0	0.3	25.0	0.9	139	0.2	2.0	0.3	32	3.23
933337	Drill Core	7.02	4.3	141.9	12.5	28	0.1	2.1	13.8	353	3.00	0.9	2.7	15.6	6.6	1618	0.2	1.4	0.3	32	3.22
933338	Drill Core	7.43	5.8	242.1	11.2	34	0.1	1.9	14.1	306	3.29	<0.5	3.5	23.4	9.7	1683	0.1	0.8	0.2	35	2.64
933339	Drill Core	7.11	5.3	178.2	12.1	35	0.1	2.3	13.2	310	3.77	2.7	4.3	20.4	9.9	527	<0.1	1.2	0.3	30	3.02
933340	Drill Core	7.77	8.6	135.1	20.6	41	0.1	2.6	12.3	353	3.73	2.2	3.4	20.1	10.3	271	0.2	2.0	0.3	25	3.76
933341	Drill Core	7.15	6.2	110.8	15.7	40	<0.1	3.0	7.7	263	3.39	1.0	4.1	7.0	11.1	195	0.1	1.9	0.2	42	3.01
933342	Drill Core	7.30	8.4	130.7	17.2	38	<0.1	3.6	16.7	330	3.75	6.8	3.9	12.9	8.0	183	0.2	4.4	0.3	22	5.41
933343	Drill Core	7.30	4.1	179.5	12.9	32	<0.1	2.6	15.6	371	3.55	151.0	2.8	25.4	7.3	177	0.2	2.4	0.3	19	5.10
933344	Drill Core	5.68	4.2	192.8	11.1	19	0.1	5.7	23.3	451	3.68	25.1	1.4	22.0	6.4	114	0.2	2.3	0.3	20	4.33
933345	Drill Core	5.84	1.5	70.5	11.8	27	<0.1	5.5	16.4	682	3.33	9.1	0.1	16.4	0.7	93	0.1	1.6	0.3	43	3.10



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.

Vancouver BC V6C 1Z7 Canada

Project:

Zymo

Report Date:

October 29, 2008

Page:

3 of 3

Part 2

CERTIFICATE OF ANALYSIS

SMI08000987.1

Method	Analyte	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
		P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
Unit		%	ppm	ppm	%	ppm	%	ppm	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm
MDL		0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.01	0.1	0.01	0.1	0.05	1	0.5
933328	Drill Core	0.156	31	5	1.15	50	0.009	2	1.86	0.096	0.20	<0.1	0.07	3.5	0.3	2.41	7	3.9
933329	Drill Core	0.165	26	3	0.91	82	0.004	1	1.31	0.065	0.16	<0.1	0.13	2.5	0.2	1.55	6	2.2
933330	Rock Pulp	0.114	6	187	1.13	38	0.004	6	1.09	0.055	0.39	0.5	1.32	6.6	0.2	2.95	3	8.4
933331	Drill Core	0.155	22	2	0.89	39	0.002	1	1.39	0.080	0.21	<0.1	0.13	2.8	0.3	2.63	5	4.2
933332	Drill Core	0.157	18	3	0.74	58	0.001	3	1.15	0.113	0.22	<0.1	0.19	3.0	0.3	2.32	3	4.4
933333	Drill Core	0.148	39	3	0.59	38	0.001	2	1.29	0.092	0.29	<0.1	0.07	2.2	0.3	3.81	3	6.5
933334	Drill Core	0.130	22	5	0.55	26	0.001	2	1.15	0.089	0.26	0.1	0.04	3.9	0.3	3.50	3	6.6
933335	Drill Core	0.139	12	7	0.56	80	0.001	<1	1.43	0.117	0.26	<0.1	0.02	6.6	0.3	2.73	4	6.3
933336	Drill Core	0.070	4	3	0.41	65	0.002	3	1.39	0.087	0.34	<0.1	0.03	6.1	0.4	2.49	3	5.1
933337	Drill Core	0.122	19	2	0.66	76	0.002	3	1.67	0.092	0.37	<0.1	0.04	3.0	0.4	2.81	4	3.7
933338	Drill Core	0.152	33	3	0.89	68	0.002	1	1.58	0.093	0.23	<0.1	0.03	2.1	0.3	3.23	4	4.8
933339	Drill Core	0.162	22	3	0.79	35	0.002	2	1.74	0.080	0.28	<0.1	0.03	2.2	0.3	3.64	4	6.1
933340	Drill Core	0.163	20	2	0.77	31	0.002	3	1.28	0.078	0.30	<0.1	0.03	2.1	0.4	3.46	3	4.5
933341	Drill Core	0.158	28	2	0.97	45	0.002	3	1.39	0.084	0.20	<0.1	0.05	2.7	0.3	2.26	6	2.0
933342	Drill Core	0.178	10	2	0.74	45	0.001	2	1.07	0.093	0.27	<0.1	0.02	3.1	0.3	2.95	3	3.9
933343	Drill Core	0.182	6	2	0.53	77	0.001	4	1.54	0.091	0.26	<0.1	0.03	3.4	0.3	2.95	3	4.2
933344	Drill Core	0.134	5	2	0.47	69	0.001	2	1.75	0.098	0.24	<0.1	0.02	3.4	0.2	3.29	3	5.3
933345	Drill Core	0.044	5	4	0.53	81	0.003	3	2.11	0.134	0.21	<0.1	<0.01	5.3	0.2	1.37	5	1.2

QUALITY CONTROL REPORT

SMI08000987.1

Method	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
Unit	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	
MDL	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	
Pulp Duplicates																					
933329	Drill Core	8.43	20.2	405.7	14.8	51	0.1	2.5	9.2	241	2.70	<0.5	3.4	20.7	10.3	445	0.3	0.3	0.2	43	1.86
REP 933329	QC		21.3	419.1	15.3	52	0.1	2.2	9.2	247	2.77	<0.5	3.6	19.5	11.1	466	0.3	0.3	0.2	43	1.92
Core Reject Duplicates																					
933317	Drill Core	5.91	71.7	1832	85.5	212	1.2	8.5	20.0	342	2.80	13.8	0.6	84.7	1.0	39	1.8	1.5	0.5	19	0.95
DUP 933317	QC		69.2	1923	84.8	206	1.2	7.5	20.3	348	2.78	14.2	0.6	108.7	1.0	38	2.0	1.4	0.5	20	0.89
Reference Materials																					
STD DS7	Standard		19.9	108.2	78.5	415	0.9	52.8	8.7	621	2.30	50.8	5.5	59.5	5.1	81	6.4	6.8	5.2	80	0.95
STD DS7	Standard		21.2	107.4	84.7	417	0.9	54.7	8.9	638	2.41	52.7	6.1	75.0	5.6	89	6.6	7.0	5.5	79	1.01
STD DS7	Standard		21.4	118.9	66.9	383	0.8	59.5	10.4	614	2.35	49.6	4.6	84.7	4.1	67	6.1	5.8	4.2	78	0.94
STD DS7	Standard		22.0	114.4	66.1	387	0.8	56.7	10.0	622	2.36	47.7	4.6	80.3	4.2	69	6.1	5.7	4.2	81	0.97
STD DS7	Standard		20.0	106.8	61.8	400	0.8	55.0	9.0	621	2.41	48.2	4.4	62.2	3.9	65	5.8	5.0	4.0	85	0.97
STD DS7	Standard		21.1	105.8	60.0	396	0.9	56.6	9.1	621	2.39	49.8	4.1	70.9	3.8	68	5.2	4.8	3.9	81	0.99
STD DS7 Expected			20.9	109	70.6	411	0.9	56	9.7	627	2.39	48.2	4.9	70	4.4	69	6.4	5.9	4.5	86	0.93
BLK	Blank		<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01
BLK	Blank		<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	0.12
BLK	Blank		<0.1	0.9	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01
Prep Wash																					
G1	Prep Blank	<0.01	0.7	30.6	2.0	49	<0.1	4.7	5.2	628	2.16	0.5	1.7	13.3	4.0	58	<0.1	<0.1	<0.1	43	0.55
G1	Prep Blank	<0.01	0.8	27.1	1.7	43	<0.1	4.5	4.8	555	1.92	<0.5	1.5	7.0	3.4	53	<0.1	<0.1	<0.1	38	0.50

QUALITY CONTROL REPORT

SMI08000987.1

Method		1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
Analyte		P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se	
Unit		%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
MDL		0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5	
Pulp Duplicates																			
933329	Drill Core	0.165	26	3	0.91	82	0.004	1	1.31	0.065	0.16	<0.1	0.13	2.5	0.2	1.55	6	2.2	
REP 933329	QC	0.157	26	3	0.92	73	0.004	2	1.33	0.065	0.18	<0.1	0.14	2.8	0.2	1.58	6	1.9	
Core Reject Duplicates																			
933317	Drill Core	0.010	4	3	0.22	64	<0.001	2	0.98	0.066	0.37	<0.1	0.15	1.9	0.3	1.71	3	2.5	
DUP 933317	QC	0.009	4	4	0.22	64	0.001	2	1.05	0.069	0.40	<0.1	0.14	2.1	0.3	1.68	3	2.7	
Reference Materials																			
STD DS7	Standard	0.078	14	176	1.03	398	0.125	39	1.00	0.083	0.44	4.5	0.20	2.4	4.4	0.19	5	3.2	
STD DS7	Standard	0.080	15	176	1.08	403	0.125	40	1.03	0.090	0.45	4.6	0.21	2.4	4.7	0.19	5	4.0	
STD DS7	Standard	0.073	11	187	1.02	352	0.130	37	0.97	0.080	0.41	3.8	0.18	2.5	3.5	0.19	4	3.3	
STD DS7	Standard	0.076	12	187	1.01	350	0.132	39	1.00	0.082	0.41	3.8	0.18	2.7	3.8	0.20	4	3.7	
STD DS7	Standard	0.075	12	186	1.00	360	0.113	41	0.97	0.083	0.42	4.1	0.18	2.5	4.1	0.19	5	3.9	
STD DS7	Standard	0.071	13	192	1.01	356	0.119	39	0.99	0.084	0.42	4.2	0.18	2.6	3.8	0.19	5	3.4	
STD DS7 Expected		0.08	13	163	1.05	370	0.124	39	0.959	0.073	0.44	3.8	0.2	2.5	4.2	0.21	4.6	3.5	
BLK	Blank	<0.001	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5	
BLK	Blank	<0.001	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5	
BLK	Blank	<0.001	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5	
Prep Wash																			
G1	Prep Blank	0.091	7	14	0.68	269	0.167	<1	1.08	0.065	0.59	<0.1	<0.01	2.8	0.3	<0.05	5	<0.5	
G1	Prep Blank	0.081	6	13	0.59	223	0.143	<1	0.95	0.059	0.53	<0.1	<0.01	2.6	0.4	<0.05	4	<0.5	



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.

Vancouver BC V6C 1Z7 Canada

Submitted By:

Glen Garratt

Receiving Lab:

Canada-Smithers

Received:

October 03, 2008

Report Date:

October 20, 2008

Page:

1 of 2

CERTIFICATE OF ANALYSIS

SMI08001009.1

CLIENT JOB INFORMATION

Project: Zymo
Shipment ID: zy-rk-08-19
P.O. Number
Number of Samples: 7

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
DISP-RJT Dispose of Reject After 90 days

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Mincord Exploration Consultants Ltd.
110 - 325 Howe St.
Vancouver BC V6C 1Z7
Canada

CC: Bob Johnston

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status
R150	7	Crush, split and pulverize rock to 200 mesh		
1DX15	7	1:1:1 Aqua Regia digestion ICP-MS analysis	15	Completed

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only. All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.

** asterisk indicates that an analytical result could not be provided due to unusually high levels of interference from other elements.



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.

Vancouver BC V6C 1Z7 Canada

Project:

Zymo

Report Date:

October 20, 2008

Page:

2 of 2

Part 1

CERTIFICATE OF ANALYSIS

SMI08001009.1

Method	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
Unit	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	
MDL	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	
726817	Rock	1.59	1.2	15.0	6.4	140	<0.1	7.8	6.9	539	2.72	11.3	<0.1	0.6	0.8	11	0.5	2.1	0.2	39	0.32
726818	Rock	1.30	0.2	13.1	24.0	45	<0.1	8.5	6.1	376	1.76	0.6	0.3	2.1	0.8	57	<0.1	0.1	<0.1	23	1.58
726819	Rock	1.49	9.2	392.4	8.5	29	0.4	8.5	37.6	215	9.00	1.9	0.2	54.0	0.7	67	<0.1	0.9	1.4	75	1.38
726820	Rock	0.74	1.0	219.2	14.8	51	0.1	7.9	12.7	218	4.90	1.9	1.0	50.1	4.2	129	0.2	0.3	0.8	126	1.44
726821	Rock	2.12	6.9	1540	10.1	37	1.4	8.5	17.0	242	4.00	1.1	0.3	97.1	0.5	30	0.2	0.2	0.3	199	1.27
726822	Rock	0.31	1.7	70.2	63.0	68	0.6	6.1	8.2	445	7.95	5.7	<0.1	16.2	0.7	15	0.1	2.1	3.3	91	0.10
726823	Rock	0.40	27.8	285.4	13.9	38	0.5	6.6	9.2	333	5.20	3.0	0.6	9.9	1.7	11	0.3	0.7	2.1	58	0.24



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
 Report Date: October 20, 2008

Page: 2 of 2 Part 2

CERTIFICATE OF ANALYSIS

SMI08001009.1

Method	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se	
Unit	%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
MDL	0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5	
726817	Rock	0.041	7	11	0.30	104	0.002	1	0.92	0.032	0.19	<0.1	0.02	3.9	0.1	0.18	4	<0.5
726818	Rock	0.072	12	13	0.58	160	0.001	1	0.95	0.050	0.13	<0.1	0.02	1.6	<0.1	<0.05	5	<0.5
726819	Rock	0.091	9	11	0.81	15	0.006	1	2.09	0.238	0.17	<0.1	0.03	8.8	<0.1	7.77	9	7.0
726820	Rock	0.222	15	5	2.06	76	0.021	2	3.14	0.197	0.11	<0.1	0.07	8.7	<0.1	2.24	11	1.0
726821	Rock	0.140	4	25	0.98	41	0.199	4	2.32	0.114	0.15	1.1	0.02	14.4	<0.1	1.43	10	1.8
726822	Rock	0.078	4	16	0.80	93	0.002	<1	2.59	0.069	0.17	0.2	0.02	7.2	<0.1	1.60	6	3.3
726823	Rock	0.095	8	14	0.51	81	0.002	1	1.97	0.064	0.16	<0.1	0.02	4.1	<0.1	1.99	6	2.0

QUALITY CONTROL REPORT

SMI08001009.1

Method	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
Unit	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	
MDL	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	
Reference Materials																					
STD DS7	Standard	19.9	104.9	70.8	425	0.8	55.3	9.1	651	2.37	50.8	5.0	78.2	4.3	68	6.1	5.9	4.2	87	1.00	
STD DS7	Standard	20.5	105.1	70.4	420	0.8	55.7	8.8	635	2.45	51.6	4.7	67.1	4.3	70	6.4	6.2	4.3	89	1.02	
STD DS7	Standard	21.3	111.9	78.4	404	0.9	61.8	9.6	620	2.29	47.6	5.4	65.7	4.7	71	6.0	5.9	4.1	79	0.93	
STD DS7	Standard	22.8	117.1	77.9	450	0.9	59.8	9.7	645	2.37	48.4	5.4	67.3	5.0	74	5.7	6.1	4.7	81	0.98	
STD DS7 Expected		20.9	109	70.6	411	0.9	56	9.7	627	2.39	48.2	4.9	70	4.4	69	6.4	5.9	4.5	86	0.93	
BLK	Blank	<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01	
BLK	Blank	<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01	
Prep Wash																					
G1	Prep Blank	<0.01	0.4	3.2	5.2	63	<0.1	4.6	4.8	569	2.06	<0.5	1.9	0.6	4.2	61	<0.1	<0.1	0.2	38	0.56
G1	Prep Blank	<0.01	0.9	2.3	38.2	51	0.1	4.6	4.7	579	1.99	0.7	1.7	<0.5	3.9	54	<0.1	0.1	0.4	38	0.50

QUALITY CONTROL REPORT

SMI08001009.1

Method		1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte		P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
Unit		%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm
MDL		0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5
Reference Materials																		
STD DS7	Standard	0.075	12	169	1.07	366	0.107	39	1.02	0.079	0.44	4.5	0.19	2.2	4.5	0.20	5	3.8
STD DS7	Standard	0.076	14	173	1.08	384	0.116	42	1.06	0.085	0.42	4.9	0.21	2.3	4.4	0.21	5	4.0
STD DS7	Standard	0.069	13	187	1.00	358	0.127	35	0.95	0.076	0.40	4.0	0.20	2.3	4.3	0.18	4	3.9
STD DS7	Standard	0.073	14	189	1.02	367	0.134	40	0.97	0.079	0.41	4.2	0.23	2.4	4.2	0.19	5	3.7
STD DS7 Expected		0.08	13	163	1.05	370	0.124	39	0.959	0.073	0.44	3.8	0.2	2.5	4.2	0.21	4.6	3.5
BLK	Blank	<0.001	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
BLK	Blank	<0.001	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
Prep Wash																		
G1	Prep Blank	0.071	9	11	0.59	234	0.155	1	1.04	0.079	0.53	0.2	<0.01	2.2	0.3	<0.05	5	<0.5
G1	Prep Blank	0.073	8	11	0.59	225	0.149	1	0.94	0.054	0.51	0.2	<0.01	1.9	0.4	<0.05	5	<0.5



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.

Vancouver BC V6C 1Z7 Canada

Submitted By:

Glen Garratt

Receiving Lab:

Canada-Smithers

Received:

October 03, 2008

Report Date:

October 20, 2008

Page:

1 of 3

CERTIFICATE OF ANALYSIS

SMI08001010.1

CLIENT JOB INFORMATION

Project: Zymo
Shipment ID: zy-co-08-10
P.O. Number
Number of Samples: 37

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
DISP-RJT Dispose of Reject After 90 days

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Mincord Exploration Consultants Ltd.
110 - 325 Howe St.
Vancouver BC V6C 1Z7
Canada

CC: Bob Johnston

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status
R150	36	Crush split and pulverize drill core to 200 mesh		
1DX15	37	1:1:1 Aqua Regia digestion ICP-MS analysis	15	Completed

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only. All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.

** asterisk indicates that an analytical result could not be provided due to unusually high levels of interference from other elements.



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
 Report Date: October 20, 2008

Page: 2 of 3 Part 1

CERTIFICATE OF ANALYSIS

SMI08001010.1

Method	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
Unit	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	
MDL	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	
933346	Drill Core	5.62	1.0	65.1	8.5	40	<0.1	5.5	13.6	1162	5.01	2.6	0.1	8.6	0.7	84	<0.1	0.6	0.2	52	2.68
933347	Drill Core	5.23	22.6	1204	15.0	67	0.4	6.7	20.9	401	3.54	0.8	2.8	47.9	9.0	78	0.2	0.2	0.5	53	1.95
933348	Drill Core	7.12	24.7	1492	16.4	54	0.5	3.7	19.7	364	3.34	1.3	3.1	86.6	9.0	95	0.3	<0.1	0.1	41	2.33
933349	Drill Core	7.09	47.7	1395	15.3	57	0.4	4.5	18.3	362	3.82	2.4	2.5	85.9	8.4	173	0.3	<0.1	0.1	55	3.27
933350	Drill Core	7.68	134.2	1474	15.8	52	0.5	4.0	21.1	296	3.59	2.0	2.8	70.6	8.1	251	0.3	<0.1	0.1	52	3.17
933351	Drill Core	7.43	52.4	1207	14.2	48	0.4	4.3	23.1	302	3.68	4.9	2.0	54.8	5.7	400	0.3	0.2	0.2	38	4.40
933352	Drill Core	7.76	28.3	1072	8.6	43	0.4	4.4	23.4	282	4.45	8.1	1.4	48.5	3.9	226	0.1	0.1	0.1	68	3.65
933353	Drill Core	7.52	30.4	1360	8.7	45	0.3	3.7	20.4	323	3.99	2.9	1.4	63.2	3.8	217	0.2	0.2	<0.1	73	4.50
933354	Drill Core	6.46	54.3	1735	10.3	60	0.4	5.9	21.9	355	4.42	6.0	1.2	77.5	4.3	110	0.2	0.2	0.2	109	2.40
933355	Drill Core	7.32	105.6	1732	9.0	55	0.5	5.9	25.8	359	4.75	5.9	1.4	103.1	3.3	120	0.3	<0.1	<0.1	135	2.75
933356	Drill Core	7.48	23.7	2070	8.3	57	0.6	8.5	28.3	375	4.87	7.0	0.9	87.6	2.7	133	0.2	0.1	0.1	166	2.61
933357	Drill Core	8.61	65.8	1589	9.6	56	0.5	6.1	24.0	352	4.68	3.8	1.2	66.7	3.7	89	0.3	<0.1	<0.1	106	2.63
933358	Drill Core	7.78	16.1	1882	8.2	54	0.5	4.6	20.7	313	4.66	3.1	1.4	88.5	4.6	144	0.3	0.1	<0.1	90	2.81
933359	Drill Core	7.18	13.6	1882	9.4	54	0.5	4.9	22.8	329	4.57	2.3	1.1	89.7	4.6	363	0.3	0.5	<0.1	80	2.57
933360	Rock Pulp	0.09	7.2	3235	13.3	129	0.6	145.1	14.1	838	5.62	11.9	0.2	229.3	1.4	179	0.7	7.9	0.4	58	2.82
933361	Drill Core	7.86	6.2	2012	9.3	62	0.6	4.1	21.5	338	4.48	3.1	1.3	95.0	4.7	112	0.4	0.2	<0.1	88	2.54
933362	Drill Core	7.75	9.2	1878	7.2	52	0.4	4.8	22.1	314	4.65	3.5	1.5	102.4	3.8	129	0.2	0.2	<0.1	105	2.69
933363	Drill Core	7.21	66.2	1080	12.6	49	0.3	6.4	12.7	748	3.22	7.4	0.7	65.6	1.5	372	0.2	1.2	<0.1	47	2.91
933364	Drill Core	7.29	24.2	1552	18.6	57	0.5	10.0	15.1	739	3.63	3.3	0.8	100.8	1.1	193	0.2	0.3	0.2	48	2.32
933365	Drill Core	6.95	35.4	1516	17.4	52	0.5	10.6	11.1	657	3.35	3.1	1.1	280.4	1.1	274	0.2	0.6	0.1	55	2.38
933366	Drill Core	7.86	37.5	736.7	16.1	38	0.3	6.1	7.0	747	2.22	4.2	1.9	74.1	1.2	119	0.2	0.9	<0.1	27	2.65
933367	Drill Core	8.66	47.9	980.6	16.5	31	0.3	7.1	8.8	846	2.31	13.3	0.5	80.8	1.4	83	0.2	4.6	<0.1	20	2.16
933368	Drill Core	6.65	44.9	1023	14.3	48	0.3	7.2	8.6	580	2.51	5.3	0.4	75.7	1.3	115	0.2	5.2	0.1	40	1.81
933369	Drill Core	7.03	45.7	2433	11.5	60	0.6	7.7	17.3	478	4.18	2.3	0.9	174.7	3.9	199	0.4	1.7	0.1	71	2.03
933370	Drill Core	6.72	183.7	1869	16.2	60	0.6	7.6	14.8	604	3.44	4.1	0.4	105.1	1.4	126	0.3	4.7	0.1	60	1.79
933371	Drill Core	6.97	48.3	1043	10.1	40	0.3	10.0	12.3	995	3.12	1.4	0.4	89.1	1.4	34	0.2	0.2	0.2	51	0.92
933372	Drill Core	7.65	59.6	683.6	11.6	39	0.2	7.8	8.0	660	2.51	0.6	0.4	56.8	1.4	34	0.3	0.1	0.1	49	1.02
933373	Drill Core	8.16	45.3	1077	9.9	55	0.4	7.9	12.1	764	3.26	0.7	0.4	58.7	1.4	38	0.2	<0.1	0.2	67	1.47
933374	Drill Core	7.61	20.6	1763	13.2	67	0.6	7.1	19.6	518	4.16	9.1	0.7	91.6	3.4	58	0.3	0.2	0.2	74	1.88
933375	Drill Core	7.27	17.2	1804	10.3	57	0.6	5.8	21.9	558	4.04	1.0	1.3	111.7	4.4	82	0.2	<0.1	0.1	67	2.06

This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
Report Date: October 20, 2008

Page: 2 of 3 **Part** 2

CERTIFICATE OF ANALYSIS

SMI08001010.1

Method	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se	
Unit	%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
MDL	0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5	
933346	Drill Core	0.061	7	6	0.77	93	0.004	2	3.09	0.136	0.12	<0.1	<0.01	4.8	<0.1	1.11	7	1.5
933347	Drill Core	0.161	37	10	1.01	112	0.010	1	1.68	0.039	0.30	3.8	0.05	2.3	0.3	1.69	6	5.1
933348	Drill Core	0.167	31	4	0.81	120	0.003	2	1.44	0.026	0.24	0.1	0.07	2.0	0.3	1.74	5	3.9
933349	Drill Core	0.168	28	5	0.96	100	0.004	2	1.80	0.034	0.34	0.2	0.07	2.6	0.2	1.54	6	4.1
933350	Drill Core	0.176	32	6	1.07	76	0.004	2	1.79	0.043	0.29	0.6	0.05	2.3	0.1	2.21	7	5.0
933351	Drill Core	0.167	16	5	0.86	85	0.004	3	1.86	0.027	0.36	0.7	0.05	2.9	0.2	2.10	5	4.3
933352	Drill Core	0.176	19	5	1.18	113	0.047	2	2.34	0.041	0.56	0.4	0.08	4.8	0.5	1.97	7	3.4
933353	Drill Core	0.172	19	5	1.17	129	0.053	2	2.11	0.078	0.44	<0.1	0.05	5.2	0.3	1.61	7	3.8
933354	Drill Core	0.181	10	7	1.68	40	0.210	1	2.43	0.140	0.15	0.8	0.04	6.6	<0.1	1.84	9	5.0
933355	Drill Core	0.167	9	11	1.79	52	0.215	1	2.76	0.203	0.28	0.2	0.05	8.8	0.2	2.36	9	3.8
933356	Drill Core	0.153	9	14	2.09	47	0.272	2	2.91	0.192	0.33	0.2	0.05	11.5	0.2	2.41	10	4.3
933357	Drill Core	0.167	12	7	1.48	27	0.146	3	2.46	0.162	0.26	0.4	0.04	6.1	0.2	1.91	9	4.4
933358	Drill Core	0.185	14	6	1.63	71	0.087	2	2.47	0.115	0.28	<0.1	0.05	4.9	0.1	1.88	9	3.6
933359	Drill Core	0.174	18	6	1.42	107	0.064	1	2.29	0.099	0.47	<0.1	0.08	4.6	0.4	1.87	9	4.8
933360	Rock Pulp	0.115	6	178	1.16	48	0.002	5	1.11	0.054	0.37	0.6	1.28	6.1	<0.1	2.85	3	8.9
933361	Drill Core	0.178	14	4	1.55	61	0.064	1	2.17	0.089	0.22	0.2	0.06	4.1	<0.1	1.85	9	3.3
933362	Drill Core	0.175	13	8	1.58	84	0.093	2	2.45	0.123	0.41	0.1	0.03	5.7	0.2	1.98	9	4.2
933363	Drill Core	0.078	7	9	0.81	146	0.020	1	1.46	0.018	0.51	0.2	0.05	4.6	0.3	1.07	4	2.2
933364	Drill Core	0.069	6	12	0.85	110	0.006	<1	1.77	0.027	0.51	0.1	0.05	5.1	0.3	1.14	5	2.1
933365	Drill Core	0.088	7	12	0.80	207	0.022	<1	1.49	0.024	0.51	<0.1	0.02	5.5	0.3	0.69	5	1.2
933366	Drill Core	0.035	5	5	0.43	253	0.002	2	1.21	0.020	0.53	<0.1	0.05	4.2	0.2	0.55	3	1.1
933367	Drill Core	0.042	5	4	0.55	167	0.002	2	0.96	0.020	0.62	<0.1	0.06	4.2	0.3	0.69	2	1.6
933368	Drill Core	0.053	9	11	0.76	248	0.004	2	1.00	0.044	0.38	0.1	0.07	5.9	0.1	0.69	4	1.4
933369	Drill Core	0.135	18	9	1.17	128	0.034	2	1.82	0.066	0.44	0.1	0.06	5.2	0.3	1.45	7	3.9
933370	Drill Core	0.052	11	10	0.81	127	0.005	1	1.42	0.033	0.36	0.2	0.06	4.3	0.1	1.17	6	2.3
933371	Drill Core	0.059	11	11	0.71	163	0.009	<1	1.85	0.045	0.59	0.2	0.02	4.2	0.2	1.15	5	1.7
933372	Drill Core	0.062	11	11	0.65	157	0.007	<1	1.47	0.055	0.48	0.1	0.02	4.5	0.2	1.12	5	1.7
933373	Drill Core	0.043	8	9	0.96	92	0.049	1	1.58	0.061	0.45	0.3	<0.01	6.2	0.5	1.15	5	1.8
933374	Drill Core	0.167	10	6	1.47	52	0.116	2	2.53	0.171	0.52	0.4	0.02	5.5	0.6	1.46	8	3.3
933375	Drill Core	0.148	10	6	1.40	29	0.115	2	2.40	0.155	0.28	<0.1	0.01	4.8	0.3	1.67	8	3.2



AcmeLabs ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
Report Date: October 20, 2008

Page: 3 of 3 **Part** 1

CERTIFICATE OF ANALYSIS

SMI08001010.1

Method	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
Unit	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	
MDL	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	
933376	Drill Core	7.85	46.2	2356	15.7	66	0.7	6.5	22.7	428	4.13	5.5	1.1	139.0	4.6	107	0.3	0.2	0.2	67	2.00
933377	Drill Core	7.36	12.7	2245	38.7	310	0.8	6.0	19.7	484	3.96	1.4	1.2	140.9	4.8	121	3.8	0.1	0.1	63	2.30
933378	Drill Core	7.14	26.3	997.4	17.0	79	0.5	6.5	13.2	881	3.51	2.1	2.4	80.9	5.0	190	0.2	0.3	0.2	67	2.06
933379	Drill Core	7.30	24.4	607.3	19.7	97	0.3	8.1	12.2	1057	3.36	1.7	2.5	40.0	4.6	278	0.2	0.9	0.2	72	1.87
933380	Drill Core	7.00	36.3	2168	23.5	129	0.7	10.7	15.0	1069	3.58	7.7	0.6	156.2	1.4	120	1.0	9.1	0.2	46	1.57
933381	Drill Core	7.15	222.7	1697	27.4	65	0.8	6.6	12.4	660	2.61	47.8	1.2	127.2	2.2	73	0.4	95.2	0.3	20	1.57
933382	Drill Core	6.77	66.5	1618	30.6	60	0.9	5.6	9.6	765	2.20	25.6	1.6	125.1	4.0	124	0.1	36.6	0.2	16	2.45



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.

Vancouver BC V6C 1Z7 Canada

Project:

Zymo

Report Date:

October 20, 2008

Page:

3 of 3

Part 2

CERTIFICATE OF ANALYSIS

SMI08001010.1

Method	Analyte	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
		P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
Unit		%	ppm	ppm	%	ppm	%	ppm	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm
MDL		0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.05	1	0.5	0.5
933376	Drill Core	0.132	13	7	1.31	34	0.105	2	2.20	0.158	0.22	0.2	0.03	4.6	0.3	2.08	8	3.9
933377	Drill Core	0.135	14	4	1.26	45	0.065	2	2.27	0.154	0.27	<0.1	0.30	4.1	0.4	1.63	7	3.1
933378	Drill Core	0.108	22	9	0.96	148	0.017	2	1.78	0.069	0.30	0.1	0.04	4.1	0.3	0.78	6	1.2
933379	Drill Core	0.092	23	13	0.98	212	0.007	2	1.61	0.056	0.25	<0.1	0.08	5.1	0.2	0.55	6	1.2
933380	Drill Core	0.057	8	9	0.83	88	0.002	2	1.29	0.040	0.40	<0.1	0.11	5.0	0.4	0.99	4	2.4
933381	Drill Core	0.053	9	2	0.55	130	0.002	2	0.64	0.026	0.38	<0.1	0.10	3.9	0.3	0.86	2	2.9
933382	Drill Core	0.048	12	2	0.73	80	<0.001	1	0.65	0.029	0.35	<0.1	0.10	3.0	0.3	0.75	2	2.0

QUALITY CONTROL REPORT

SMI08001010.1

Method	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
Unit	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	ppm	
MDL	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	
Pulp Duplicates																					
933363	Drill Core	7.21	66.2	1080	12.6	49	0.3	6.4	12.7	748	3.22	7.4	0.7	65.6	1.5	372	0.2	1.2	<0.1	47	2.91
REP 933363	QC		65.4	1104	13.1	49	0.3	6.3	12.6	755	3.22	7.5	0.7	66.0	1.5	393	0.2	1.1	<0.1	46	2.91
933378	Drill Core	7.14	26.3	997.4	17.0	79	0.5	6.5	13.2	881	3.51	2.1	2.4	80.9	5.0	190	0.2	0.3	0.2	67	2.06
REP 933378	QC		26.3	992.4	16.4	79	0.4	6.6	13.6	874	3.58	1.9	2.3	72.7	4.9	185	0.3	0.2	0.2	67	2.10
Core Reject Duplicates																					
933367	Drill Core	8.66	47.9	980.6	16.5	31	0.3	7.1	8.8	846	2.31	13.3	0.5	80.8	1.4	83	0.2	4.6	<0.1	20	2.16
DUP 933367	QC		48.3	966.9	15.6	30	0.3	6.6	9.0	853	2.29	13.7	0.6	75.1	1.3	96	0.2	4.6	<0.1	20	2.17
Reference Materials																					
STD DS7	Standard		19.9	104.9	70.8	425	0.8	55.3	9.1	651	2.37	50.8	5.0	78.2	4.3	68	6.1	5.9	4.2	87	1.00
STD DS7	Standard		20.5	105.1	70.4	420	0.8	55.7	8.8	635	2.45	51.6	4.7	67.1	4.3	70	6.4	6.2	4.3	89	1.02
STD DS7	Standard		21.3	107.0	78.1	401	1.0	57.1	9.5	624	2.33	48.6	5.4	104.1	4.8	74	6.0	6.0	4.3	81	0.97
STD DS7	Standard		21.1	101.6	74.7	386	0.9	55.3	8.9	595	2.22	46.4	5.2	71.7	4.6	71	5.4	5.8	4.2	77	0.94
STD DS7 Expected			20.9	109	70.6	411	0.9	56	9.7	627	2.39	48.2	4.9	70	4.4	69	6.4	5.9	4.5	86	0.93
BLK	Blank		<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01
BLK	Blank		<0.1	0.7	<0.1	4	<0.1	<0.1	<0.1	<1	0.02	2.7	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01
Prep Wash																					
G1	Prep Blank	<0.01	0.8	2.6	2.2	46	<0.1	4.7	4.4	595	1.95	<0.5	1.6	3.1	3.8	47	<0.1	<0.1	<0.1	40	0.52
G1	Prep Blank	<0.01	0.6	2.7	2.2	50	<0.1	4.4	4.6	609	2.03	<0.5	1.7	1.1	4.0	60	<0.1	<0.1	<0.1	42	0.70

QUALITY CONTROL REPORT

SMI08001010.1

Method		1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
Analyte		P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se	
Unit		%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
MDL		0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5	
Pulp Duplicates																			
933363	Drill Core	0.078	7	9	0.81	146	0.020	1	1.46	0.018	0.51	0.2	0.05	4.6	0.3	1.07	4	2.2	
REP 933363	QC	0.077	7	9	0.81	147	0.021	2	1.50	0.018	0.53	0.2	0.06	4.8	0.3	1.08	4	2.0	
933378	Drill Core	0.108	22	9	0.96	148	0.017	2	1.78	0.069	0.30	0.1	0.04	4.1	0.3	0.78	6	1.2	
REP 933378	QC	0.104	22	9	0.97	155	0.016	2	1.79	0.074	0.31	0.1	0.05	4.0	0.3	0.79	7	2.1	
Core Reject Duplicates																			
933367	Drill Core	0.042	5	4	0.55	167	0.002	2	0.96	0.020	0.62	<0.1	0.06	4.2	0.3	0.69	2	1.6	
DUP 933367	QC	0.044	5	4	0.55	136	0.002	2	0.92	0.019	0.61	0.1	0.05	4.1	0.3	0.70	2	1.7	
Reference Materials																			
STD DS7	Standard	0.075	12	169	1.07	366	0.107	39	1.02	0.079	0.44	4.5	0.19	2.2	4.5	0.20	5	3.8	
STD DS7	Standard	0.076	14	173	1.08	384	0.116	42	1.06	0.085	0.42	4.9	0.21	2.3	4.4	0.21	5	4.0	
STD DS7	Standard	0.073	13	187	1.08	359	0.129	36	1.02	0.076	0.41	4.1	0.21	2.4	4.2	0.19	5	4.0	
STD DS7	Standard	0.069	14	180	1.03	349	0.123	37	0.98	0.077	0.39	3.7	0.20	2.3	4.0	0.18	4	3.8	
STD DS7 Expected		0.08	13	163	1.05	370	0.124	39	0.959	0.073	0.44	3.8	0.2	2.5	4.2	0.21	4.6	3.5	
BLK	Blank	<0.001	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5	
BLK	Blank	<0.001	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5	
Prep Wash																			
G1	Prep Blank	0.083	7	12	0.62	243	0.133	<1	1.02	0.058	0.56	0.3	<0.01	2.1	0.2	<0.05	5	<0.5	
G1	Prep Blank	0.086	8	12	0.64	256	0.135	<1	1.06	0.058	0.57	0.4	<0.01	2.1	0.3	<0.05	6	<0.5	



ACME ANALYTICAL LABORATORIES LTD.
1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.

110 - 325 Howe St.
Vancouver BC V6C 1Z7 Canada

Submitted By: Glen Garratt
Receiving Lab: Canada-Smithers
Received: October 03, 2008
Report Date: October 20, 2008
Page: 1 of 3

CERTIFICATE OF ANALYSIS

SMI08001011.1

CLIENT JOB INFORMATION

Project: Zymo
Shipment ID: zy-co-08-09
P.O. Number
Number of Samples: 37

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
DISP-RJT Dispose of Reject After 90 days

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Mincord Exploration Consultants Ltd.
110 - 325 Howe St.
Vancouver BC V6C 1Z7
Canada

CC: Bob Johnston

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status
R150	36	Crush split and pulverize drill core to 200 mesh		
1DX15	37	1:1:1 Aqua Regia digestion ICP-MS analysis	15	Completed

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.
All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.
** asterisk indicates that an analytical result could not be provided due to unusually high levels of interference from other elements.



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
 Report Date: October 20, 2008

Page: 2 of 3 Part 1

CERTIFICATE OF ANALYSIS

SMI08001011.1

Method	Analyte	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca
Unit	MDL	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm
		0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01
933396	Drill Core	6.76	73.0	817.7	15.8	37	0.2	8.3	12.1	342	2.09	58.2	2.1	72.8	4.9	536	0.2	0.6	0.1	27	2.80
933397	Drill Core	6.87	50.2	1143	17.1	37	0.4	4.4	14.1	292	2.20	5.4	4.1	87.6	9.6	814	<0.1	0.6	0.1	32	4.44
933398	Drill Core	6.98	23.1	600.2	15.6	40	0.2	3.8	14.3	283	2.84	1.8	4.9	37.5	11.3	660	0.1	0.5	0.2	52	2.93
933399	Drill Core	6.89	22.3	632.8	20.6	46	0.2	3.3	16.3	337	3.12	1.9	4.9	40.2	11.6	692	0.3	0.5	0.2	54	3.22
933400	Drill Core	7.09	16.3	491.2	24.7	46	0.4	3.7	13.6	633	3.15	4.2	3.6	46.7	11.1	526	0.2	2.3	0.2	54	3.10
933401	Drill Core	7.32	17.6	600.9	21.3	52	0.3	4.5	16.3	385	3.13	1.5	4.7	30.0	11.5	503	0.1	0.4	0.2	60	3.00
933402	Drill Core	6.93	38.9	393.4	18.1	44	0.2	3.7	13.6	431	2.74	2.4	4.3	13.9	10.9	749	0.2	0.7	0.2	41	3.19
933403	Drill Core	7.15	10.2	612.9	104.8	257	0.4	5.4	18.3	1095	3.65	16.6	2.7	35.2	5.4	142	1.6	1.9	0.8	18	3.35
933404	Drill Core	5.65	11.3	405.0	14.9	47	0.2	5.8	13.7	438	3.55	6.1	1.4	24.9	4.4	214	0.2	2.6	0.2	53	3.51
933405	Drill Core	8.44	9.8	487.8	11.1	32	0.1	7.3	22.6	464	4.74	3.7	1.0	22.6	3.9	423	0.1	0.6	0.2	65	5.44
933406	Drill Core	7.46	15.6	642.5	10.6	36	0.2	9.4	25.5	369	6.20	3.9	1.1	28.0	3.8	371	0.1	0.7	0.2	82	4.16
933407	Drill Core	7.06	8.8	381.7	14.0	37	0.2	9.1	18.1	583	4.17	5.0	0.4	13.9	1.5	135	0.1	0.9	0.2	47	2.96
933408	Drill Core	7.38	18.2	934.8	23.5	65	0.6	16.3	86.3	770	9.31	28.9	0.3	59.7	0.6	45	0.2	4.1	0.5	25	2.25
933409	Drill Core	6.70	10.4	142.6	8.9	34	0.1	8.6	18.0	632	3.80	17.9	0.4	23.7	0.7	56	<0.1	2.6	0.1	23	1.38
933410	Drill Core	6.48	37.4	235.6	7.2	26	0.1	10.5	12.2	1090	3.06	42.7	0.2	20.5	0.6	63	<0.1	2.4	0.3	28	2.79
933411	Drill Core	6.78	14.4	1429	18.7	57	0.7	21.0	69.3	709	6.86	259.2	0.5	37.0	0.9	45	0.2	3.8	0.4	22	1.79
933412	Drill Core	6.52	8.9	341.4	22.1	55	0.2	4.9	23.5	923	4.31	790.9	0.9	17.0	2.0	61	0.2	3.8	0.4	16	2.08
933413	Drill Core	7.87	16.8	529.2	26.3	61	0.2	3.1	32.5	980	4.53	694.7	0.8	14.8	2.7	181	0.2	4.5	0.4	13	3.32
933414	Drill Core	7.15	34.5	133.5	7.4	32	<0.1	8.5	8.9	655	2.45	44.2	0.3	28.2	1.5	299	<0.1	0.6	0.2	26	2.24
933415	Drill Core	7.77	13.8	221.2	12.0	28	0.1	9.2	15.6	523	3.01	5.5	0.3	26.6	1.2	156	<0.1	0.2	0.2	28	2.42
933416	Drill Core	6.01	18.8	410.7	11.7	33	0.2	12.9	20.7	569	3.89	13.1	0.4	22.6	1.2	198	<0.1	0.3	0.3	36	2.92
933417	Drill Core	5.50	29.1	239.0	7.5	27	0.1	10.6	13.6	588	3.06	11.8	0.4	21.7	1.1	185	<0.1	0.3	0.2	30	2.58
933418	Drill Core	3.65	21.9	212.0	8.6	23	0.1	10.1	14.8	620	2.77	2.4	0.3	21.9	1.0	119	<0.1	0.5	0.2	33	3.28
933419	Drill Core	7.02	18.5	245.1	9.7	39	0.1	10.7	14.9	774	3.23	5.8	0.3	19.4	1.0	169	0.2	0.8	0.5	29	2.48
933420	Rock Pulp	0.08	7.2	2996	15.1	121	0.5	128.6	13.9	767	5.39	11.7	0.2	205.2	1.5	167	0.6	7.8	0.5	52	2.75
933421	Drill Core	7.10	13.6	225.3	8.4	45	0.2	8.9	14.3	847	3.53	7.4	0.4	21.1	1.1	148	0.1	0.6	0.4	35	2.19
933422	Drill Core	6.25	12.3	298.0	11.0	40	0.2	8.5	12.6	1074	3.61	29.7	0.4	36.6	1.4	148	0.1	1.0	0.3	30	2.67
933423	Drill Core	6.69	5.0	249.8	19.7	82	0.2	9.9	21.2	1414	5.34	2.9	0.3	27.3	1.1	241	0.2	0.3	0.4	54	2.16
933424	Drill Core	6.49	13.2	611.8	15.5	78	0.3	16.3	48.8	901	8.40	0.8	0.4	45.1	1.9	161	0.3	0.2	0.4	83	1.88
933425	Drill Core	8.97	7.0	212.0	14.1	66	0.2	12.7	45.6	1023	7.57	2.4	0.5	23.3	1.4	154	0.2	0.2	0.4	64	1.77

This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
 Report Date: October 20, 2008

Page: 2 of 3 Part 2

CERTIFICATE OF ANALYSIS

SMI08001011.1

Method Analyte Unit MDL	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
	P %	La ppm	Cr ppm	Mg %	Ba ppm	Ti %	B ppm	Al %	Na %	K %	W ppm	Hg ppm	Sc ppm	Tl ppm	S %	Ga ppm	Se ppm	
933396	Drill Core	0.082	18	5	0.68	60	0.002	1	1.07	0.034	0.34	0.1	0.08	3.7	0.3	1.61	3	2.0
933397	Drill Core	0.130	21	9	0.74	40	0.001	1	1.02	0.033	0.22	0.2	0.11	2.6	0.2	2.54	3	3.3
933398	Drill Core	0.136	33	4	0.94	45	0.004	2	1.38	0.034	0.16	<0.1	0.06	2.7	0.2	1.94	5	3.7
933399	Drill Core	0.134	35	5	0.95	37	0.006	2	1.39	0.042	0.17	0.1	0.04	3.0	0.1	2.49	5	4.1
933400	Drill Core	0.139	29	4	0.86	40	0.009	2	1.36	0.041	0.20	<0.1	0.04	3.1	0.2	2.12	5	5.1
933401	Drill Core	0.137	31	5	0.97	34	0.011	<1	1.49	0.052	0.20	<0.1	0.01	2.9	0.2	2.35	5	4.4
933402	Drill Core	0.131	27	4	0.73	51	0.003	2	1.28	0.032	0.19	0.1	0.06	2.4	0.2	2.07	4	3.9
933403	Drill Core	0.117	12	3	0.78	29	0.001	2	0.95	0.027	0.28	<0.1	0.15	3.3	0.4	3.37	2	4.8
933404	Drill Core	0.126	15	5	1.12	77	0.008	2	2.15	0.061	0.25	<0.1	0.07	4.5	0.4	1.80	6	3.2
933405	Drill Core	0.143	16	7	1.22	51	0.013	2	2.26	0.080	0.21	<0.1	0.04	5.6	0.3	2.62	6	4.1
933406	Drill Core	0.139	14	9	1.61	43	0.042	2	3.41	0.261	0.22	<0.1	0.05	6.5	0.4	3.84	9	3.5
933407	Drill Core	0.074	5	7	1.08	56	0.009	2	2.28	0.162	0.42	<0.1	0.06	5.5	0.5	2.60	5	3.5
933408	Drill Core	0.132	3	4	0.63	18	0.002	2	1.20	0.062	0.37	<0.1	0.14	5.0	0.5	9.42	3	11.6
933409	Drill Core	0.027	3	5	0.45	80	0.004	2	1.55	0.051	0.57	<0.1	0.02	3.8	0.7	2.52	3	3.0
933410	Drill Core	0.063	2	6	0.91	81	0.003	2	1.44	0.058	0.57	0.1	0.05	4.3	0.6	1.92	3	2.5
933411	Drill Core	0.071	2	4	0.52	40	0.003	2	1.23	0.051	0.46	<0.1	0.12	4.2	0.6	6.45	2	8.5
933412	Drill Core	0.112	4	3	0.59	53	0.002	2	0.99	0.065	0.38	<0.1	0.08	2.5	0.5	3.69	2	7.2
933413	Drill Core	0.130	5	2	0.68	28	<0.001	2	0.91	0.061	0.23	<0.1	0.16	1.8	0.4	3.92	2	8.4
933414	Drill Core	0.036	4	5	0.60	151	0.006	3	1.91	0.077	0.66	<0.1	0.02	4.3	0.7	1.38	4	2.6
933415	Drill Core	0.045	5	5	0.65	98	0.007	2	1.88	0.109	0.45	<0.1	0.02	4.1	0.5	2.24	4	3.7
933416	Drill Core	0.039	5	7	0.77	67	0.005	3	2.15	0.093	0.36	<0.1	0.05	5.2	0.4	3.14	4	5.8
933417	Drill Core	0.055	5	6	0.62	73	0.004	3	1.87	0.116	0.42	<0.1	<0.01	4.4	0.5	2.45	3	4.3
933418	Drill Core	0.059	5	7	0.63	112	0.001	2	1.48	0.108	0.24	<0.1	0.02	4.8	0.3	1.96	3	4.0
933419	Drill Core	0.055	4	6	0.68	66	0.002	2	1.40	0.101	0.26	<0.1	0.02	4.5	0.3	1.94	3	2.8
933420	Rock Pulp	0.112	5	173	1.08	29	0.001	5	1.02	0.048	0.33	0.5	1.18	6.3	0.2	2.82	3	8.4
933421	Drill Core	0.032	3	5	0.73	90	0.003	2	1.76	0.082	0.31	<0.1	0.03	4.8	0.4	2.08	4	3.1
933422	Drill Core	0.061	5	7	0.76	99	0.002	2	1.83	0.089	0.28	0.1	0.02	4.0	0.3	1.89	4	2.3
933423	Drill Core	0.067	5	11	0.96	67	0.006	2	2.40	0.105	0.23	<0.1	0.02	4.9	0.2	2.56	6	2.7
933424	Drill Core	0.154	8	11	1.42	50	0.008	2	3.42	0.210	0.19	<0.1	0.02	7.0	0.3	5.87	10	11.1
933425	Drill Core	0.096	5	12	1.15	56	0.006	1	2.94	0.150	0.30	0.1	0.01	5.6	0.4	3.68	8	5.1



AcmeLabs ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
Report Date: October 20, 2008

Page: 3 of 3 **Part** 1

CERTIFICATE OF ANALYSIS

SMI08001011.1

Method	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
Unit	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	
MDL	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	
933426	Drill Core	7.73	8.5	246.3	19.5	61	0.2	12.9	23.8	1169	5.47	8.7	0.3	37.6	1.2	182	0.2	0.3	0.6	48	2.10
933427	Drill Core	7.03	13.9	108.9	18.7	34	0.1	9.6	10.3	807	3.50	2.1	0.4	20.9	1.3	132	0.2	0.3	0.5	29	2.13
933428	Drill Core	7.24	8.7	110.8	9.3	31	<0.1	11.0	8.6	906	2.85	4.3	0.3	13.1	1.5	136	0.1	5.6	0.4	25	2.17
933429	Drill Core	7.95	16.4	417.5	22.8	61	0.2	2.9	26.4	523	3.96	7.2	1.0	38.0	4.6	418	0.3	8.0	0.3	27	3.15
933430	Drill Core	6.47	14.9	325.4	20.1	65	0.2	2.3	14.2	456	4.44	4.3	1.2	32.1	4.9	738	0.2	0.7	0.3	26	3.13
933431	Drill Core	7.66	22.0	547.7	15.7	56	0.3	3.2	32.5	426	4.31	2.3	1.4	61.1	4.1	243	0.2	0.5	0.3	31	3.38
933432	Drill Core	6.85	12.3	278.4	9.3	38	0.2	5.7	17.7	623	2.91	17.1	0.6	28.8	2.7	285	<0.1	0.5	0.3	27	3.59



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**

110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo

Report Date: October 20, 2008

Page: 3 of 3 Part 2

CERTIFICATE OF ANALYSIS

SMI08001011.1

Method	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se	
Unit	%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
MDL	0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5	
933426	Drill Core	0.069	5	10	1.01	71	0.004	1	2.59	0.115	0.26	<0.1	0.02	5.0	0.4	3.40	7	4.9
933427	Drill Core	0.053	4	8	0.66	67	0.003	1	1.66	0.102	0.40	<0.1	0.02	4.2	0.4	2.84	4	3.7
933428	Drill Core	0.054	5	6	0.83	113	0.002	1	1.61	0.090	0.26	<0.1	0.02	4.1	0.3	1.56	4	2.3
933429	Drill Core	0.156	17	2	0.82	53	0.001	1	1.21	0.089	0.22	<0.1	0.03	2.3	0.3	3.13	4	6.8
933430	Drill Core	0.158	27	2	0.90	53	0.002	1	1.56	0.075	0.26	0.1	0.03	2.1	0.4	3.81	5	5.7
933431	Drill Core	0.152	22	<1	0.88	71	0.002	<1	1.70	0.088	0.22	<0.1	0.04	2.2	0.4	3.61	6	7.2
933432	Drill Core	0.111	11	3	0.69	129	0.002	2	1.71	0.093	0.25	<0.1	0.04	3.8	0.4	1.81	4	3.4

QUALITY CONTROL REPORT

SMI08001011.1

Method	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
Unit	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	
MDL	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	
Core Reject Duplicates																					
933404	Drill Core	5.65	11.3	405.0	14.9	47	0.2	5.8	13.7	438	3.55	6.1	1.4	24.9	4.4	214	0.2	2.6	0.2	53	3.51
DUP 933404	QC		10.7	417.4	16.0	53	0.2	6.2	14.3	433	3.69	5.7	1.4	23.2	4.6	236	0.2	2.4	0.1	56	3.56
Reference Materials																					
STD DS7	Standard		21.3	107.0	78.1	401	1.0	57.1	9.5	624	2.33	48.6	5.4	104.1	4.8	74	6.0	6.0	4.3	81	0.97
STD DS7	Standard		21.1	101.6	74.7	386	0.9	55.3	8.9	595	2.22	46.4	5.2	71.7	4.6	71	5.4	5.8	4.2	77	0.94
STD DS7	Standard		23.0	123.1	78.2	413	1.0	58.2	10.2	626	2.37	55.0	5.5	76.1	4.8	81	7.5	7.0	5.3	80	0.98
STD DS7	Standard		22.2	114.6	65.7	405	0.9	56.6	9.4	594	2.32	53.0	5.1	70.9	4.9	81	6.9	6.7	5.1	80	0.98
STD DS7 Expected			20.9	109	70.6	411	0.9	56	9.7	627	2.39	48.2	4.9	70	4.4	69	6.4	5.9	4.5	86	0.93
BLK	Blank		<0.1	0.7	<0.1	4	<0.1	<0.1	<0.1	<1	0.02	2.7	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01
BLK	Blank		<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01
Prep Wash																					
G1	Prep Blank	<0.01	0.8	6.9	3.0	49	<0.1	4.6	4.6	588	2.01	<0.5	1.8	3.2	4.2	53	<0.1	0.3	<0.1	41	0.53
G1	Prep Blank	<0.01	0.9	10.1	3.0	46	<0.1	4.3	4.5	555	1.98	<0.5	1.8	2.8	4.0	57	<0.1	0.2	<0.1	40	0.55

QUALITY CONTROL REPORT

SMI08001011.1

Method		1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte		P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
Unit		%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm
MDL		0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5
Core Reject Duplicates																		
933404	Drill Core	0.126	15	5	1.12	77	0.008	2	2.15	0.061	0.25	<0.1	0.07	4.5	0.4	1.80	6	3.2
DUP 933404	QC	0.139	16	6	1.18	92	0.010	3	2.22	0.068	0.27	<0.1	0.07	5.0	0.5	1.82	6	2.8
Reference Materials																		
STD DS7	Standard	0.073	13	187	1.08	359	0.129	36	1.02	0.076	0.41	4.1	0.21	2.4	4.2	0.19	5	4.0
STD DS7	Standard	0.069	14	180	1.03	349	0.123	37	0.98	0.077	0.39	3.7	0.20	2.3	4.0	0.18	4	3.8
STD DS7	Standard	0.072	15	195	1.04	398	0.122	38	1.01	0.080	0.44	4.2	0.20	2.8	4.2	0.18	5	4.1
STD DS7	Standard	0.077	15	168	1.03	371	0.118	40	1.03	0.085	0.42	4.0	0.19	2.5	4.2	0.18	6	3.8
STD DS7 Expected		0.08	13	163	1.05	370	0.124	39	0.959	0.073	0.44	3.8	0.2	2.5	4.2	0.21	4.6	3.5
BLK	Blank	<0.001	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
BLK	Blank	<0.001	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
Prep Wash																		
G1	Prep Blank	0.078	8	11	0.64	249	0.147	1	1.00	0.053	0.53	0.2	<0.01	2.0	0.4	<0.05	5	<0.5
G1	Prep Blank	0.077	8	10	0.61	231	0.143	1	0.99	0.058	0.51	0.2	<0.01	2.1	0.4	<0.05	5	<0.5



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.

Vancouver BC V6C 1Z7 Canada

Submitted By:

Glen Garratt

Receiving Lab:

Canada-Smithers

Received:

October 03, 2008

Report Date:

October 17, 2008

Page:

1 of 3

CERTIFICATE OF ANALYSIS

SMI08001012.1

CLIENT JOB INFORMATION

Project: Zymo
Shipment ID: zy-so-08-17
P.O. Number
Number of Samples: 53

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
DISP-RJT-SOIL Immediate Disposal of Soil Reject

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Mincord Exploration Consultants Ltd.
110 - 325 Howe St.
Vancouver BC V6C 1Z7
Canada

CC: Bob Johnston

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status
SS80	53	Dry at 60C sieve 100g to -80 mesh		
Dry at 60C	53	Dry at 60C		
1DX15	53	1:1:1 Aqua Regia digestion ICP-MS analysis	15	Completed

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only. All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.

** asterisk indicates that an analytical result could not be provided due to unusually high levels of interference from other elements.



AcmeLabs ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
Report Date: October 17, 2008

Page: 2 of 3 **Part** 1

CERTIFICATE OF ANALYSIS

SMI08001012.1

Method Analyte	Unit	MDL	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
			Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	P
			ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	%	
			0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	0.001
ZSE-08-01	Soil		3.5	93.2	44.3	254	1.2	22.5	8.7	1431	4.14	52.0	2.0	15.7	0.4	23	0.8	1.4	0.6	53	0.38	0.147
ZSE-08-02	Soil		4.4	68.9	69.9	172	0.6	12.2	9.0	629	5.14	67.5	1.1	12.3	0.2	16	0.4	2.1	0.9	89	0.24	0.085
ZSE-08-03	Soil		3.8	38.9	84.9	173	0.4	13.9	9.7	559	5.94	46.4	1.0	11.6	1.0	28	0.3	1.5	0.9	83	0.45	0.082
ZSE-08-04	Soil		6.4	76.4	53.8	155	0.7	13.1	10.6	721	5.41	62.6	1.0	15.5	0.5	14	0.4	1.8	1.1	72	0.19	0.095
ZSE-08-05	Soil		4.0	101.7	74.0	134	3.4	12.4	9.7	658	5.67	36.1	3.1	8.5	0.4	25	0.7	2.2	0.6	48	0.29	0.287
ZSE-08-06	Soil		2.9	50.9	43.2	125	0.4	11.1	5.1	192	3.78	49.3	0.8	12.6	0.2	19	0.3	2.0	1.1	87	0.25	0.049
ZSE-08-07	Soil		3.3	125.7	142.7	298	0.9	20.4	19.3	1589	6.31	106.5	1.3	31.2	1.8	13	0.5	3.0	1.5	72	0.12	0.107
ZSE-08-10	Soil		3.6	79.7	57.2	99	0.8	10.6	7.5	512	7.40	73.5	1.4	41.3	0.9	24	0.3	2.1	1.2	140	0.12	0.108
ZSE-08-11	Soil		3.9	99.0	52.1	136	1.3	13.4	10.1	487	5.80	78.5	1.5	26.7	0.2	10	0.3	2.3	1.1	92	0.07	0.094
ZSE-08-12	Soil		3.8	104.0	52.4	137	1.2	13.4	10.0	484	5.78	78.6	1.6	10.4	0.2	10	0.3	2.5	1.2	88	0.07	0.096
ZSE-08-13	Soil		5.6	87.9	44.4	115	0.6	14.1	9.0	428	7.11	99.4	1.3	26.6	0.3	9	0.3	2.7	1.2	93	0.05	0.099
ZSE-08-14	Soil		6.7	114.0	89.5	137	1.0	14.9	7.0	400	6.28	101.0	0.8	23.0	0.1	6	0.2	2.1	1.7	88	0.03	0.121
ZSE-08-15	Soil		7.2	147.5	83.4	209	1.6	14.3	15.3	1944	6.85	117.9	1.0	155.8	1.3	7	0.5	2.0	1.4	70	0.04	0.157
ZSE-08-16	Soil		6.7	172.1	88.5	268	1.1	15.9	12.9	847	6.14	107.8	0.9	28.7	1.7	7	0.5	2.5	1.6	63	0.04	0.103
ZSE-08-17	Soil		6.4	129.9	87.3	144	1.4	14.0	7.8	424	5.64	73.6	0.8	26.9	0.5	12	0.2	1.6	1.2	67	0.08	0.116
ZSE-08-18	Soil		1.4	69.6	37.9	29	2.8	5.7	3.4	113	0.46	4.0	1.9	5.6	0.3	13	0.4	0.7	0.2	8	0.12	0.421
ZSE-08-19	Soil		4.5	52.9	32.6	74	0.5	11.5	10.7	1915	5.00	38.3	0.9	4.7	0.2	45	0.4	1.2	0.4	93	0.27	0.076
ZSE-08-20	Soil		11.2	102.6	39.6	139	0.4	11.3	7.4	743	4.22	78.3	0.9	19.8	0.2	25	0.3	1.8	1.1	76	0.14	0.080
ZSE-08-22	Soil		1.7	29.5	24.8	96	1.0	17.2	6.0	225	4.50	38.5	0.7	5.6	0.6	14	0.2	1.9	0.6	72	0.06	0.055
ZSE-08-23	Soil		3.8	60.8	48.0	120	0.3	13.6	6.5	265	5.01	81.2	0.9	12.5	2.4	15	0.3	3.3	0.8	86	0.04	0.053
ZSE-08-24	Soil		2.0	36.1	49.8	131	0.5	14.7	6.8	354	4.99	150.8	0.8	6.3	0.5	13	0.7	2.2	0.8	87	0.04	0.063
ZSE-08-25	Soil		1.5	42.8	47.7	246	1.0	10.0	6.9	1236	5.83	200.7	0.9	6.6	0.5	12	0.9	3.6	2.1	73	0.06	0.077
ZSE-08-26	Soil		1.8	34.0	37.7	88	0.6	16.1	6.4	453	6.57	62.4	0.6	3.0	1.1	15	0.3	2.2	0.6	94	0.03	0.079
ZSE-08-27	Soil		1.4	40.8	24.8	148	0.3	20.6	10.3	543	4.37	44.7	1.1	5.9	0.5	21	0.3	2.6	0.5	78	0.11	0.050
ZSE-08-28	Soil		2.0	62.5	129.2	455	0.5	20.9	14.7	1044	6.54	196.8	1.4	31.4	2.0	19	0.7	4.4	1.6	82	0.09	0.094
ZSE-08-29	Soil		2.0	45.9	161.1	299	0.3	15.7	9.2	590	6.14	109.2	0.9	36.7	1.7	13	0.7	3.7	1.4	71	0.05	0.110
ZSE-08-30	Soil		1.5	35.5	76.8	144	0.3	8.7	5.8	688	4.69	81.9	0.5	6.9	0.2	12	0.2	5.0	1.0	64	0.08	0.092
ZSE-08-31	Soil		1.2	20.6	28.4	86	0.8	8.1	4.0	202	4.29	29.2	0.5	3.4	1.0	10	0.2	1.8	0.3	77	0.02	0.066
ZSE-08-32	Soil		1.5	30.5	60.8	154	1.0	10.0	6.7	1033	5.91	46.5	0.6	3.0	0.6	11	0.4	1.9	0.6	80	0.02	0.091
ZSE-08-33	Soil		2.1	42.4	74.9	187	0.9	9.9	5.4	356	6.70	87.8	0.8	80.2	1.5	14	0.4	3.0	1.1	85	0.10	0.056

This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.



AcmeLabs ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
Report Date: October 17, 2008

Page: 2 of 3 **Part** 2

CERTIFICATE OF ANALYSIS

SMI08001012.1

Method	Analyte	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
		La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
Unit		ppm	ppm	%	ppm	%	ppm	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
MDL		1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.05	1	0.05	
ZSE-08-01	Soil	34	18	0.18	111	0.009	2	2.70	0.008	0.08	0.2	0.31	5.3	0.3	<0.05	8	2.2
ZSE-08-02	Soil	14	20	0.19	103	0.009	1	1.89	0.006	0.07	0.1	0.08	1.9	0.3	<0.05	8	0.8
ZSE-08-03	Soil	8	25	0.30	109	0.007	2	2.64	0.007	0.08	0.2	0.08	2.9	0.2	<0.05	8	0.9
ZSE-08-04	Soil	10	19	0.31	107	0.007	1	1.98	0.007	0.09	0.1	0.06	2.2	0.2	<0.05	7	1.1
ZSE-08-05	Soil	13	18	0.17	143	0.007	2	2.31	0.006	0.08	0.1	0.27	1.1	0.2	0.09	7	2.2
ZSE-08-06	Soil	10	18	0.15	195	0.012	1	1.38	0.005	0.11	0.1	0.04	1.8	0.2	<0.05	9	0.8
ZSE-08-07	Soil	11	22	0.39	69	0.010	2	2.36	0.007	0.10	0.1	0.15	4.3	0.3	<0.05	6	2.0
ZSE-08-10	Soil	19	28	0.30	59	0.090	1	2.15	0.020	0.06	0.1	0.10	4.0	0.1	0.08	16	1.7
ZSE-08-11	Soil	12	17	0.36	52	0.019	1	1.81	0.008	0.07	0.1	0.13	2.0	0.2	0.10	9	1.4
ZSE-08-12	Soil	13	18	0.37	53	0.028	3	1.86	0.009	0.08	0.1	0.10	2.3	0.2	0.13	9	1.7
ZSE-08-13	Soil	11	20	0.30	52	0.016	<1	1.96	0.009	0.08	0.1	0.09	2.4	0.2	0.08	11	1.5
ZSE-08-14	Soil	9	18	0.07	50	0.008	2	0.99	0.004	0.07	<0.1	0.11	1.0	0.3	0.09	9	1.5
ZSE-08-15	Soil	10	20	0.26	119	0.009	2	2.56	0.006	0.07	0.1	0.11	3.3	0.3	<0.05	8	1.7
ZSE-08-16	Soil	8	20	0.26	118	0.004	1	2.17	0.006	0.07	<0.1	0.10	3.7	0.3	<0.05	6	2.0
ZSE-08-17	Soil	7	20	0.18	90	0.009	3	1.48	0.005	0.09	0.1	0.12	2.1	0.3	0.08	7	1.8
ZSE-08-18	Soil	13	10	0.07	71	0.006	2	1.87	0.008	0.05	<0.1	0.16	2.3	0.1	0.25	1	4.5
ZSE-08-19	Soil	8	23	0.20	138	0.015	2	1.44	0.006	0.06	0.1	0.09	1.6	0.2	<0.05	10	1.2
ZSE-08-20	Soil	13	17	0.08	151	0.007	1	1.17	0.006	0.08	0.1	0.05	1.5	0.2	<0.05	6	1.2
ZSE-08-22	Soil	7	31	0.34	87	0.020	4	2.93	0.007	0.08	0.2	0.08	3.3	0.2	0.06	9	1.2
ZSE-08-23	Soil	7	32	0.23	73	0.018	3	3.65	0.005	0.07	0.1	0.20	3.8	0.3	<0.05	9	0.9
ZSE-08-24	Soil	7	25	0.26	82	0.010	2	2.21	0.006	0.08	0.1	0.13	2.5	0.3	<0.05	9	0.7
ZSE-08-25	Soil	12	17	0.10	145	0.008	2	1.91	0.006	0.08	0.2	0.14	3.5	0.3	<0.05	7	0.6
ZSE-08-26	Soil	6	38	0.29	68	0.013	2	2.63	0.006	0.08	<0.1	0.09	3.4	0.2	<0.05	10	0.8
ZSE-08-27	Soil	9	25	0.41	133	0.017	3	2.01	0.007	0.10	<0.1	0.14	4.2	0.1	<0.05	6	0.8
ZSE-08-28	Soil	18	27	0.36	149	0.012	3	2.72	0.007	0.09	0.1	0.17	6.2	0.3	<0.05	9	1.5
ZSE-08-29	Soil	7	24	0.27	110	0.008	2	2.43	0.006	0.07	0.1	0.12	3.5	0.2	<0.05	7	0.8
ZSE-08-30	Soil	8	14	0.08	97	0.007	1	1.08	0.003	0.05	0.1	0.08	1.2	0.2	<0.05	7	<0.5
ZSE-08-31	Soil	6	18	0.12	67	0.010	<1	1.34	0.004	0.03	0.1	0.07	2.2	0.2	<0.05	7	<0.5
ZSE-08-32	Soil	6	22	0.18	81	0.010	2	1.83	0.004	0.05	0.2	0.12	2.2	0.3	<0.05	9	<0.5
ZSE-08-33	Soil	6	19	0.19	88	0.008	1	1.66	0.004	0.04	0.1	0.11	3.4	0.2	<0.05	8	0.6

This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.



AcmeLabs ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
Report Date: October 17, 2008

Page: 3 of 3 **Part** 1

CERTIFICATE OF ANALYSIS

SMI08001012.1

Method	Analyte	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
		Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	P
Unit		ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	%
MDL		0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	2	0.01	0.001	
ZSE-08-34	Soil	1.5	51.1	49.1	220	0.6	22.9	11.3	719	4.20	40.9	1.2	7.7	0.7	25	0.5	2.5	0.5	67	0.25	0.064
ZSE-08-35	Soil	2.1	56.0	58.0	133	0.9	9.1	4.0	212	6.03	69.8	0.9	12.2	0.5	15	0.7	3.1	1.1	100	0.12	0.050
ZSE-08-36	Soil	2.0	75.6	145.8	359	5.4	21.9	16.4	3655	4.64	76.2	2.2	14.8	1.2	20	1.9	3.0	1.0	54	0.20	0.147
ZSE-08-37	Soil	1.9	62.3	134.2	209	0.4	15.5	9.6	950	8.72	218.5	1.2	19.7	0.5	10	0.8	4.3	2.6	78	0.03	0.099
ZSE-08-38	Soil	2.5	56.2	117.4	209	0.5	15.5	12.3	1051	7.72	123.6	1.2	17.6	0.8	12	0.6	3.7	1.7	92	0.04	0.080
ZSE-08-39	Soil	1.5	62.9	79.4	182	0.8	15.5	9.9	803	5.16	62.3	1.2	17.2	1.6	13	0.8	2.6	0.8	62	0.05	0.102
ZSE-08-40	Soil	1.6	36.0	68.8	145	0.9	10.0	5.7	555	7.91	76.4	0.8	5.7	1.6	9	0.6	2.2	1.0	76	0.03	0.099
ZSE-08-41	Soil	1.7	46.6	75.8	302	0.4	19.7	13.6	885	4.43	51.9	1.6	17.8	2.7	14	0.7	1.7	0.9	64	0.05	0.076
ZSE-08-42	Soil	1.8	29.0	33.2	94	0.2	6.4	3.4	212	3.49	46.7	0.7	3.6	0.4	10	0.2	1.7	0.6	105	0.08	0.047
ZSE-08-43	Soil	2.5	28.9	66.5	118	0.3	9.2	8.1	823	5.05	55.2	1.0	11.4	2.0	11	0.2	2.1	1.0	79	0.03	0.047
ZSE-08-44	Soil	2.1	58.0	122.4	256	1.8	12.1	7.9	536	4.48	68.4	1.2	22.4	2.1	12	0.6	2.2	1.4	49	0.05	0.047
ZSE-08-45	Soil	2.2	46.1	139.3	221	0.7	14.8	9.8	623	6.38	81.1	1.1	16.3	2.4	13	0.9	2.5	1.4	68	0.06	0.059
ZSE-08-46	Soil	1.9	15.9	7.2	87	0.3	5.8	3.5	154	2.59	29.0	0.4	22.9	0.8	7	0.1	2.3	0.3	67	0.03	0.026
ZSE-08-47	Soil	2.7	41.6	53.3	167	0.6	9.0	5.5	441	7.10	102.7	0.7	7.3	2.0	9	0.3	3.3	1.8	112	0.02	0.095
ZSE-08-48	Soil	2.4	44.2	46.9	140	0.6	9.7	5.2	435	4.81	76.3	0.7	43.3	0.3	19	0.4	2.5	1.3	67	0.05	0.043
ZSE-08-49	Soil	3.3	61.3	73.3	240	2.8	10.1	8.5	338	4.89	101.0	0.8	12.5	1.9	5	0.4	2.6	1.7	54	0.02	0.042
ZSE-08-50	Soil	1.9	58.6	87.5	184	0.8	10.7	11.9	893	4.94	57.4	0.7	6.4	0.6	16	0.9	2.1	1.2	69	0.23	0.055
ZSE-08-51	Soil	2.4	34.2	39.2	118	0.5	10.0	4.1	191	4.01	58.7	0.8	14.3	0.3	9	0.3	2.0	1.0	48	0.02	0.059
ZSE-08-52	Soil	2.3	35.4	19.6	134	0.2	8.4	4.3	194	3.71	51.6	0.6	7.7	1.1	12	0.3	2.3	0.6	83	0.02	0.029
ZSE-08-53	Soil	1.6	18.7	25.9	96	0.3	5.5	4.0	179	3.08	30.7	0.6	3.5	0.9	5	0.2	1.4	0.9	61	0.01	0.037
ZSE-08-54	Soil	2.4	66.7	68.9	179	0.6	15.4	7.4	519	5.71	50.5	1.1	31.1	1.4	11	0.6	2.0	0.7	48	0.04	0.096
ZSE-08-55	Soil	2.6	39.8	117.9	184	0.5	7.1	5.9	486	6.12	59.1	0.7	16.4	2.2	7	1.1	1.7	1.3	55	0.03	0.114
ZSE-08-56	Soil	3.2	73.0	207.2	353	1.7	10.0	13.7	3074	8.23	151.5	1.1	25.2	1.5	12	1.2	3.7	3.1	57	0.14	0.436



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
 Report Date: October 17, 2008

Page: 3 of 3 Part 2

CERTIFICATE OF ANALYSIS

SMI08001012.1

Method	Analyte	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
		La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
Unit		ppm	ppm	%	ppm	%	ppm	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
MDL		1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.01	0.01	0.01	0.05	1	0.5	
ZSE-08-34	Soil	16	22	0.37	190	0.006	2	2.17	0.005	0.09	0.1	0.16	4.9	0.2	<0.05	7	0.8
ZSE-08-35	Soil	8	18	0.08	135	0.014	1	1.22	0.004	0.04	0.2	0.14	2.2	0.2	<0.05	11	0.6
ZSE-08-36	Soil	37	22	0.23	216	0.005	1	3.02	0.006	0.07	0.2	0.51	6.9	0.3	<0.05	6	1.5
ZSE-08-37	Soil	8	25	0.18	118	0.013	1	2.49	0.005	0.03	0.2	0.23	2.7	0.2	0.05	9	1.1
ZSE-08-38	Soil	11	22	0.24	104	0.013	2	2.58	0.005	0.05	0.1	0.21	3.3	0.2	<0.05	9	1.3
ZSE-08-39	Soil	8	25	0.25	105	0.009	3	3.04	0.006	0.05	0.1	0.28	3.8	0.2	<0.05	5	1.0
ZSE-08-40	Soil	6	21	0.16	66	0.007	1	2.71	0.005	0.04	0.1	0.25	2.7	0.2	<0.05	9	0.9
ZSE-08-41	Soil	10	26	0.35	134	0.006	3	3.60	0.006	0.08	0.1	0.20	4.4	0.3	<0.05	6	0.6
ZSE-08-42	Soil	7	15	0.06	46	0.017	3	0.83	0.004	0.05	0.1	0.10	1.5	0.2	<0.05	10	<0.5
ZSE-08-43	Soil	8	18	0.19	64	0.011	2	1.80	0.007	0.04	0.1	0.12	3.0	0.2	<0.05	8	0.6
ZSE-08-44	Soil	11	16	0.21	111	0.003	1	2.27	0.005	0.08	<0.1	0.16	3.3	0.3	<0.05	5	0.8
ZSE-08-45	Soil	7	19	0.16	81	0.009	2	2.65	0.005	0.04	0.2	0.22	3.3	0.2	<0.05	7	0.9
ZSE-08-46	Soil	8	11	0.03	24	0.007	3	0.56	0.003	0.03	0.1	0.05	1.4	0.2	<0.05	5	<0.5
ZSE-08-47	Soil	8	18	0.12	54	0.009	<1	1.80	0.004	0.05	0.1	0.12	3.3	0.2	<0.05	14	0.5
ZSE-08-48	Soil	9	14	0.09	88	0.009	2	1.16	0.004	0.04	0.1	0.07	1.8	0.2	<0.05	6	0.6
ZSE-08-49	Soil	11	11	0.17	100	0.002	1	2.15	0.005	0.05	0.1	0.11	3.2	0.3	<0.05	7	0.9
ZSE-08-50	Soil	8	16	0.11	119	0.009	2	1.56	0.005	0.08	0.2	0.15	2.4	0.2	0.05	7	0.7
ZSE-08-51	Soil	8	12	0.11	72	0.005	<1	1.53	0.005	0.04	0.2	0.19	1.4	0.2	0.06	7	1.0
ZSE-08-52	Soil	6	13	0.06	45	0.010	2	0.88	0.005	0.04	0.2	0.08	2.3	0.2	<0.05	7	<0.5
ZSE-08-53	Soil	8	11	0.06	35	0.012	3	0.79	0.004	0.04	0.2	0.06	1.5	0.2	<0.05	6	<0.5
ZSE-08-54	Soil	8	21	0.25	85	0.008	2	2.93	0.005	0.05	0.2	0.22	2.9	0.2	<0.05	6	0.9
ZSE-08-55	Soil	8	15	0.08	56	0.006	<1	2.72	0.004	0.04	0.1	0.15	2.4	0.3	<0.05	7	0.7
ZSE-08-56	Soil	8	16	0.15	93	0.007	<1	2.68	0.004	0.05	0.2	0.27	2.9	0.2	<0.05	7	1.4

QUALITY CONTROL REPORT

SMI08001012.1

Method	Analyte	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
		Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	P
Unit		ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	%	
MDL		0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	0.001
Pulp Duplicates																					
ZSE-08-22	Soil	1.7	29.5	24.8	96	1.0	17.2	6.0	225	4.50	38.5	0.7	5.6	0.6	14	0.2	1.9	0.6	72	0.06	0.055
REP ZSE-08-22	QC	1.5	29.3	25.2	92	0.9	17.1	6.1	232	4.56	38.9	0.7	5.8	0.6	14	0.3	1.7	0.7	73	0.06	0.055
ZSE-08-43	Soil	2.5	28.9	66.5	118	0.3	9.2	8.1	823	5.05	55.2	1.0	11.4	2.0	11	0.2	2.1	1.0	79	0.03	0.047
REP ZSE-08-43	QC	2.5	27.2	64.4	113	0.3	8.9	7.9	819	5.04	52.7	1.0	10.0	2.0	11	0.1	2.2	1.0	76	0.03	0.045
ZSE-08-55	Soil	2.6	39.8	117.9	184	0.5	7.1	5.9	486	6.12	59.1	0.7	16.4	2.2	7	1.1	1.7	1.3	55	0.03	0.114
REP ZSE-08-55	QC	2.5	39.7	114.5	183	0.5	6.9	5.6	477	6.07	57.9	0.7	14.2	2.1	7	0.9	1.7	1.3	55	0.03	0.111
Reference Materials																					
STD DS7	Standard	21.6	105.0	68.4	388	0.9	56.4	9.3	607	2.38	48.8	5.1	69.3	4.8	79	6.2	6.0	4.6	89	1.00	0.076
STD DS7	Standard	19.7	107.8	65.3	399	0.8	55.6	9.5	637	2.39	51.2	4.8	60.8	4.5	73	6.5	5.9	4.5	80	1.01	0.081
STD DS7 Expected		20.9	109	70.6	411	0.9	56	9.7	627	2.39	48.2	4.9	70	4.4	69	6.4	5.9	4.5	86	0.93	0.08
BLK	Blank	<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01	<0.001
BLK	Blank	<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01	<0.001

QUALITY CONTROL REPORT

SMI08001012.1

Method	Analyte	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
		La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
Unit		ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm
MDL		1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.01	0.05	1	0.5
Pulp Duplicates																	
ZSE-08-22	Soil	7	31	0.34	87	0.020	4	2.93	0.007	0.08	0.2	0.08	3.3	0.2	0.06	9	1.2
REP ZSE-08-22	QC	7	31	0.35	89	0.022	3	3.04	0.009	0.09	0.2	0.08	3.4	0.2	<0.05	9	1.1
ZSE-08-43	Soil	8	18	0.19	64	0.011	2	1.80	0.007	0.04	0.1	0.12	3.0	0.2	<0.05	8	0.6
REP ZSE-08-43	QC	8	17	0.18	62	0.009	2	1.74	0.006	0.04	0.1	0.14	2.9	0.2	<0.05	7	<0.5
ZSE-08-55	Soil	8	15	0.08	56	0.006	<1	2.72	0.004	0.04	0.1	0.15	2.4	0.3	<0.05	7	0.7
REP ZSE-08-55	QC	8	15	0.08	58	0.005	<1	2.77	0.004	0.04	0.1	0.15	2.4	0.2	<0.05	7	0.7
Reference Materials																	
STD DS7	Standard	14	190	1.04	369	0.129	43	1.02	0.088	0.44	4.3	0.20	2.4	4.4	0.17	5	3.7
STD DS7	Standard	13	187	1.03	353	0.113	41	1.02	0.086	0.44	3.8	0.19	2.3	4.1	0.18	5	3.7
STD DS7 Expected		13	163	1.05	370	0.124	39	0.959	0.073	0.44	3.8	0.2	2.5	4.2	0.21	5	3.5
BLK	Blank	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
BLK	Blank	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.

Vancouver BC V6C 1Z7 Canada

Submitted By:

Glen Garratt

Receiving Lab:

Canada-Smithers

Received:

October 06, 2008

Report Date:

October 21, 2008

Page:

1 of 3

CERTIFICATE OF ANALYSIS

SMI08001023.1

CLIENT JOB INFORMATION

Project: Zymo
Shipment ID: zy-co-08-11
P.O. Number
Number of Samples: 50

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status
R150	48	Crush split and pulverize drill core to 200 mesh		
1DX15	50	1:1:1 Aqua Regia digestion ICP-MS analysis	15	Completed

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
DISP-RJT Dispose of Reject After 90 days

ADDITIONAL COMMENTS

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Mincord Exploration Consultants Ltd.
110 - 325 Howe St.
Vancouver BC V6C 1Z7
Canada

CC: Bob Johnston



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only. All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.

“**” asterisk indicates that an analytical result could not be provided due to unusually high levels of interference from other elements.



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.

110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo

Report Date: October 21, 2008

Page: 2 of 3 Part 1

CERTIFICATE OF ANALYSIS

SMI08001023.1

Method	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
Unit	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	
MDL	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	
933383	Drill Core	6.83	35.2	1880	42.0	106	1.0	6.5	12.7	672	2.70	14.8	1.3	100.8	3.1	298	0.5	33.6	0.3	31	1.79
933384	Drill Core	7.12	33.5	1504	33.8	131	1.0	5.6	15.4	976	2.76	13.0	1.8	130.8	2.0	236	0.5	24.4	0.3	34	2.61
933385	Drill Core	7.37	50.2	3156	17.0	70	1.2	9.3	27.9	649	5.21	3.1	0.4	197.5	0.9	111	0.3	0.9	0.5	73	1.84
933386	Drill Core	7.35	29.8	2366	13.4	63	0.9	8.0	25.3	517	4.52	4.1	1.4	141.8	4.0	138	0.4	0.9	0.3	99	2.42
933387	Drill Core	7.48	47.4	2319	8.6	45	0.7	7.8	18.8	443	3.46	2.1	1.4	133.4	3.0	100	0.2	1.4	0.3	82	2.21
933388	Drill Core	5.99	31.5	1637	11.4	57	0.5	9.0	12.8	437	3.22	3.3	1.6	88.6	2.1	206	0.3	0.4	0.2	69	2.07
933389	Drill Core	8.04	41.0	2122	13.5	60	0.7	7.9	18.1	427	4.15	2.5	2.3	125.3	5.5	216	0.3	0.3	0.2	99	3.03
933390	Rock Pulp	0.04	8.2	3064	15.3	128	0.6	161.2	14.7	778	5.64	12.2	0.2	230.9	1.5	176	0.6	7.6	0.5	56	2.82
933391	Drill Core	6.75	22.3	1831	21.3	70	0.7	5.9	16.0	353	3.69	3.7	3.5	175.6	8.4	685	0.3	0.4	0.3	65	2.68
933392	Drill Core	6.34	43.1	1674	11.1	51	0.5	6.6	19.4	451	3.80	2.9	1.6	145.9	4.7	329	0.2	0.5	0.2	72	2.46
933393	Drill Core	6.58	30.1	1292	14.2	52	0.4	8.6	19.4	638	4.30	2.2	0.4	74.9	1.2	177	0.2	0.4	0.2	48	1.24
933394	Drill Core	6.75	54.4	709.5	10.8	34	0.2	6.8	11.0	587	2.76	7.1	0.4	53.7	1.3	237	0.1	0.6	0.2	25	2.30
933395	Drill Core	7.04	24.1	264.7	10.6	28	<0.1	7.7	9.1	432	1.80	30.5	0.4	31.7	1.5	203	0.2	0.8	0.2	17	1.94
933433	Drill Core	6.43	4.1	247.7	4.0	39	<0.1	11.1	15.2	796	3.36	1.6	0.3	19.6	1.3	143	<0.1	0.1	0.2	41	1.97
933434	Drill Core	4.27	30.8	375.2	9.5	59	0.2	12.6	23.4	828	8.45	2.9	0.4	31.7	1.0	285	0.1	0.2	0.3	74	2.88
933435	Drill Core	3.27	7.1	1291	8.9	67	1.4	12.7	24.3	596	5.38	4.7	0.4	54.8	1.6	121	0.2	2.3	1.2	51	3.03
933436	Drill Core	6.97	11.9	1649	8.4	57	1.7	11.9	24.7	432	5.88	24.3	0.4	72.6	2.5	127	0.3	3.9	1.2	67	2.69
933437	Drill Core	5.21	13.0	395.4	7.6	33	0.3	7.4	10.8	371	3.40	6.3	0.7	27.4	4.5	152	0.1	0.8	1.5	45	3.11
933438	Drill Core	7.91	13.7	437.2	6.8	29	0.3	4.8	6.0	320	2.72	<0.5	0.2	27.1	1.5	187	0.1	0.5	1.1	23	3.35
933439	Drill Core	6.03	10.8	373.2	5.9	31	0.3	3.8	5.0	287	2.19	1.0	0.2	20.2	1.5	565	0.1	<0.1	0.6	34	1.77
933440	Drill Core	7.60	22.0	758.6	9.2	32	0.7	5.1	7.3	318	2.45	<0.5	0.2	40.3	1.5	167	0.2	0.1	0.6	33	1.54
933441	Drill Core	7.19	11.0	1501	10.4	46	1.2	9.6	21.8	424	5.05	2.5	0.3	97.6	1.9	649	0.2	0.1	1.0	130	1.69
933442	Drill Core	6.19	11.5	832.4	12.8	48	0.7	6.4	18.3	419	4.23	1.4	0.5	44.7	2.0	159	0.2	0.2	1.0	98	1.82
933443	Drill Core	7.20	13.3	757.4	7.1	52	0.7	5.0	15.9	469	4.40	1.6	0.5	37.3	2.2	101	0.1	0.2	0.8	101	2.08
933444	Drill Core	7.00	16.5	359.7	5.8	47	0.3	5.1	12.3	439	3.39	1.2	0.6	11.2	2.4	119	0.1	0.2	0.3	83	1.91
933445	Drill Core	5.40	8.6	440.8	6.3	51	0.3	5.1	15.4	461	3.73	1.1	0.7	16.2	2.4	156	0.3	0.2	0.4	90	2.19
933446	Drill Core	6.32	26.1	336.2	5.3	37	0.2	6.6	9.0	382	2.78	2.1	0.3	8.5	1.5	114	0.1	0.3	0.2	48	1.92
933447	Drill Core	6.87	7.8	383.0	6.0	39	0.3	11.6	15.1	408	3.91	1.9	0.2	15.2	1.0	76	0.1	0.4	0.3	97	1.63
933448	Drill Core	6.95	4.7	658.2	8.9	57	0.3	12.0	16.7	457	4.54	0.5	0.3	19.9	1.5	109	0.5	0.4	0.2	88	2.54
933449	Drill Core	5.70	4.8	434.8	10.3	47	0.2	12.4	14.5	454	4.52	1.5	0.3	14.2	1.7	96	0.1	0.3	0.7	95	2.38

This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
 Report Date: October 21, 2008

Page: 2 of 3 Part 2

CERTIFICATE OF ANALYSIS

SMI08001023.1

Method	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se	
Unit	%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
MDL	0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5	
933383	Drill Core	0.050	11	4	0.70	117	0.006	2	1.13	0.024	0.43	<0.1	0.09	4.2	0.4	0.96	4	2.4
933384	Drill Core	0.059	12	4	0.59	129	0.003	2	1.11	0.022	0.32	<0.1	0.11	3.3	0.3	0.95	4	2.0
933385	Drill Core	0.041	5	6	0.81	75	0.005	1	1.84	0.037	0.32	<0.1	0.06	3.5	0.3	1.63	7	3.1
933386	Drill Core	0.150	14	6	1.35	94	0.066	3	2.27	0.090	0.55	0.2	0.09	6.8	0.6	1.65	9	3.9
933387	Drill Core	0.108	12	8	1.19	144	0.049	2	1.96	0.063	0.49	<0.1	0.08	6.0	0.5	1.08	7	2.9
933388	Drill Core	0.085	12	13	0.97	134	0.020	1	1.65	0.069	0.29	<0.1	0.08	4.7	0.2	0.90	7	2.1
933389	Drill Core	0.167	20	6	1.68	139	0.042	2	2.35	0.083	0.37	<0.1	0.09	5.8	0.4	1.33	10	2.9
933390	Rock Pulp	0.113	6	206	1.12	35	0.002	5	1.20	0.049	0.37	0.6	1.24	6.4	0.2	2.90	3	8.6
933391	Drill Core	0.127	22	2	1.18	147	0.026	2	1.90	0.042	0.35	<0.1	0.09	4.6	0.3	1.05	8	2.3
933392	Drill Core	0.112	13	7	1.24	155	0.049	2	2.00	0.061	0.51	<0.1	0.06	5.8	0.4	1.11	7	2.2
933393	Drill Core	0.060	9	11	1.07	130	0.005	2	1.92	0.046	0.43	<0.1	0.04	4.2	0.3	1.20	6	2.3
933394	Drill Core	0.067	5	6	0.80	197	0.002	2	1.23	0.028	0.42	<0.1	0.11	4.6	0.4	0.85	4	1.3
933395	Drill Core	0.055	4	3	0.53	236	0.002	2	1.05	0.024	0.58	<0.1	0.06	3.9	0.5	0.77	3	1.2
933433	Drill Core	0.068	6	7	0.97	157	0.005	2	2.23	0.080	0.32	<0.1	0.01	4.5	0.4	1.11	6	1.7
933434	Drill Core	0.127	9	12	1.07	45	0.004	1	2.60	0.076	0.23	<0.1	0.03	5.9	0.3	4.63	9	5.1
933435	Drill Core	0.138	10	13	0.72	41	0.002	3	1.17	0.028	0.21	0.7	0.02	6.8	0.2	2.72	4	2.2
933436	Drill Core	0.130	10	17	0.80	46	0.004	4	1.56	0.053	0.20	0.5	0.02	6.7	0.2	2.85	5	3.4
933437	Drill Core	0.074	11	10	0.79	110	0.001	3	1.25	0.039	0.17	0.3	0.01	4.2	0.1	1.70	5	1.8
933438	Drill Core	0.040	9	7	0.67	50	0.002	1	1.09	0.048	0.19	0.1	0.01	4.2	0.2	1.45	3	1.9
933439	Drill Core	0.043	6	9	0.92	203	0.051	3	1.54	0.129	0.17	0.2	<0.01	5.3	0.1	0.78	4	1.0
933440	Drill Core	0.045	6	8	0.85	87	0.080	1	1.34	0.103	0.14	0.2	0.01	5.1	0.1	1.13	4	2.1
933441	Drill Core	0.093	7	18	1.30	43	0.256	5	2.28	0.113	0.13	0.3	0.02	9.0	0.1	2.22	8	3.0
933442	Drill Core	0.100	8	11	1.07	28	0.208	2	2.02	0.096	0.14	0.2	0.03	6.9	<0.1	1.71	8	2.5
933443	Drill Core	0.095	8	8	1.21	28	0.204	3	2.42	0.076	0.15	0.2	0.03	6.7	0.1	1.37	8	1.7
933444	Drill Core	0.111	8	9	1.39	66	0.212	3	2.53	0.170	0.16	0.2	0.03	9.3	0.1	0.99	8	1.7
933445	Drill Core	0.090	8	7	1.45	35	0.244	2	3.20	0.249	0.16	0.2	0.03	8.6	0.2	1.30	9	2.2
933446	Drill Core	0.049	6	8	1.01	36	0.153	3	2.20	0.188	0.25	0.2	0.02	6.6	0.3	0.91	6	1.3
933447	Drill Core	0.048	7	18	0.92	57	0.146	3	2.00	0.160	0.18	0.2	<0.01	7.9	0.2	1.63	6	2.5
933448	Drill Core	0.064	8	17	0.95	49	0.087	3	2.29	0.191	0.20	0.1	<0.01	6.4	0.2	2.00	7	3.2
933449	Drill Core	0.063	8	20	0.87	65	0.105	3	2.32	0.179	0.25	0.1	<0.01	7.5	0.2	1.39	7	2.5

This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**

110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo

Report Date: October 21, 2008

Page: 3 of 3 Part 1

CERTIFICATE OF ANALYSIS

SMI08001023.1

Method	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
Unit	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	
MDL	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	
933450	Rock Pulp	0.04	8.4	3149	17.1	138	0.6	158.2	15.4	846	5.79	12.0	0.3	267.5	1.8	200	0.6	9.6	0.5	57	2.85
933451	Drill Core	6.85	12.9	395.6	7.8	42	0.2	9.9	14.6	427	3.96	1.0	0.3	12.6	1.5	82	0.1	0.1	0.6	88	1.97
933452	Drill Core	6.88	9.4	1575	9.7	86	1.2	8.4	20.3	538	5.51	5.5	0.5	77.0	1.6	80	0.4	0.2	1.2	97	2.15
933453	Drill Core	7.54	7.3	1126	4.2	59	1.6	8.6	14.6	431	4.56	3.1	0.3	81.7	1.5	54	0.2	0.2	0.8	112	1.16
933454	Drill Core	7.07	3.7	829.1	7.6	60	1.0	8.5	16.0	429	4.37	10.7	0.3	66.4	1.7	83	0.2	9.2	1.6	86	1.92
933455	Drill Core	5.72	3.8	740.3	7.5	45	0.7	6.1	15.8	351	4.20	2.2	0.3	42.9	2.3	46	0.2	0.4	0.4	91	1.23
933456	Drill Core	8.11	4.0	770.5	10.5	61	1.0	6.8	16.6	437	4.31	9.6	0.2	34.8	1.7	92	0.4	1.4	0.7	79	1.96
933457	Drill Core	5.65	5.2	1026	13.6	61	1.1	7.6	18.0	345	4.42	4.0	0.4	51.9	2.0	54	0.3	0.6	0.9	85	1.22
933488	Drill Core	7.77	28.5	339.3	13.4	37	0.4	5.7	8.1	213	2.20	1.6	1.0	22.6	5.3	25	0.2	0.7	0.7	29	1.46
933489	Drill Core	6.82	32.2	442.5	11.1	32	0.5	7.2	9.3	207	2.22	1.5	1.2	25.6	5.4	30	0.2	0.2	0.7	34	1.08
933490	Drill Core	7.68	22.0	198.6	7.4	25	0.2	3.4	4.2	190	1.48	1.4	1.6	9.7	5.4	48	0.2	0.3	0.9	30	1.31
933491	Drill Core	6.94	31.2	157.5	8.8	26	0.2	3.2	3.2	250	1.82	10.7	2.3	9.1	5.8	84	0.1	20.4	0.7	16	2.21
933492	Drill Core	7.37	17.6	703.6	9.3	34	0.5	9.7	16.2	291	4.36	173.8	0.5	39.9	1.2	74	0.1	95.6	1.3	51	2.41
933493	Drill Core	8.14	11.6	290.1	4.8	31	0.2	8.0	14.2	375	5.05	1.8	0.8	13.0	1.0	85	<0.1	0.5	0.4	131	1.57
933494	Drill Core	6.56	19.7	306.5	6.3	30	0.3	10.7	14.6	275	4.73	2.7	0.4	47.6	1.1	60	0.1	0.6	1.0	109	1.69
933495	Drill Core	7.58	16.7	312.0	6.0	31	0.3	10.4	12.5	245	4.17	47.6	0.4	25.1	1.2	39	<0.1	1.3	0.9	98	1.29
933496	Drill Core	7.34	7.1	340.3	7.8	37	0.3	13.1	15.9	282	4.81	1.6	0.3	22.3	1.0	56	0.2	0.5	0.8	121	1.28
933497	Drill Core	7.15	10.6	314.7	7.2	38	0.3	10.0	18.7	349	5.40	10.6	0.5	16.9	0.9	81	0.1	3.3	1.1	121	1.89
933498	Drill Core	8.75	8.9	133.7	7.3	34	0.1	7.8	11.6	337	4.60	<0.5	0.2	6.3	0.8	81	0.1	0.2	0.4	129	1.39
933499	Drill Core	7.01	3.0	278.5	5.6	35	0.2	8.7	11.8	375	4.78	21.7	0.2	18.4	0.8	78	0.1	0.2	0.4	132	1.26



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
 Report Date: October 21, 2008

Page: 3 of 3 Part 2

CERTIFICATE OF ANALYSIS

SMI08001023.1

Method	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se	
Unit	%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
MDL	0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5	
933450	Rock Pulp	0.117	6	208	1.15	41	0.002	5	1.28	0.055	0.41	0.5	1.30	6.6	0.2	2.87	3	7.5
933451	Drill Core	0.083	8	19	0.84	32	0.104	3	1.82	0.127	0.17	0.2	0.01	6.9	0.1	1.07	7	2.2
933452	Drill Core	0.067	7	17	1.18	38	0.159	3	2.39	0.102	0.19	0.3	0.02	7.4	0.2	2.15	9	2.7
933453	Drill Core	0.062	5	23	1.21	74	0.272	2	2.09	0.122	0.53	0.3	0.02	10.4	0.5	1.18	9	2.3
933454	Drill Core	0.056	6	16	0.99	51	0.158	<1	1.74	0.113	0.30	0.4	0.01	8.2	0.3	1.51	7	2.3
933455	Drill Core	0.067	7	13	0.98	22	0.147	1	1.60	0.082	0.17	0.1	<0.01	6.6	0.2	1.58	7	1.6
933456	Drill Core	0.054	7	18	1.00	77	0.057	2	1.74	0.078	0.29	<0.1	0.01	5.9	0.2	1.58	7	2.6
933457	Drill Core	0.077	10	17	0.89	22	0.074	2	1.60	0.091	0.20	<0.1	0.02	5.8	0.2	1.92	7	2.7
933488	Drill Core	0.032	8	8	0.39	26	0.045	1	0.80	0.051	0.18	0.4	<0.01	2.6	0.2	1.41	3	1.9
933489	Drill Core	0.024	5	11	0.45	28	0.067	2	0.88	0.073	0.11	0.5	<0.01	2.5	0.1	1.46	4	1.8
933490	Drill Core	0.033	8	7	0.48	30	0.052	2	1.08	0.113	0.12	0.2	0.01	2.4	0.1	0.56	3	0.9
933491	Drill Core	0.032	8	3	0.62	176	0.007	2	1.13	0.103	0.16	<0.1	0.01	1.8	0.2	0.76	3	0.8
933492	Drill Core	0.061	6	11	0.60	42	0.013	1	1.18	0.055	0.21	0.1	0.03	5.1	0.2	2.60	4	2.0
933493	Drill Core	0.066	5	19	1.20	102	0.260	2	2.92	0.212	0.96	<0.1	<0.01	13.2	1.4	1.51	10	1.5
933494	Drill Core	0.095	5	23	0.99	54	0.183	4	2.07	0.172	0.47	0.2	<0.01	10.5	0.6	2.55	8	2.5
933495	Drill Core	0.046	3	20	0.82	43	0.167	3	1.85	0.155	0.34	0.2	<0.01	9.1	0.5	2.16	7	2.5
933496	Drill Core	0.071	3	23	0.92	41	0.225	1	2.55	0.242	0.36	0.1	<0.01	12.3	0.5	2.22	9	1.7
933497	Drill Core	0.220	7	17	1.09	53	0.210	2	3.13	0.289	0.60	0.1	<0.01	11.9	0.8	2.54	10	1.6
933498	Drill Core	0.068	3	17	1.08	78	0.240	2	2.99	0.306	0.77	<0.1	<0.01	13.2	1.0	1.43	10	0.9
933499	Drill Core	0.066	3	19	1.23	73	0.254	<1	3.01	0.283	0.75	<0.1	<0.01	13.6	1.0	1.56	10	1.2

QUALITY CONTROL REPORT

SMI08001023.1

Method	Analyte	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca
Unit		kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%
MDL		0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01
Pulp Duplicates																					
933395	Drill Core	7.04	24.1	264.7	10.6	28	<0.1	7.7	9.1	432	1.80	30.5	0.4	31.7	1.5	203	0.2	0.8	0.2	17	1.94
REP 933395	QC		23.7	271.5	10.9	29	<0.1	7.0	8.7	441	1.79	31.3	0.5	22.9	1.5	211	0.2	0.7	0.2	18	1.94
933492	Drill Core	7.37	17.6	703.6	9.3	34	0.5	9.7	16.2	291	4.36	173.8	0.5	39.9	1.2	74	0.1	95.6	1.3	51	2.41
REP 933492	QC		16.8	644.9	8.7	32	0.6	9.3	14.7	264	4.09	166.6	0.5	37.7	1.2	72	0.2	96.2	1.3	48	2.25
Core Reject Duplicates																					
933437	Drill Core	5.21	13.0	395.4	7.6	33	0.3	7.4	10.8	371	3.40	6.3	0.7	27.4	4.5	152	0.1	0.8	1.5	45	3.11
DUP 933437	QC		13.4	417.3	7.4	34	0.3	8.0	11.0	388	3.37	6.2	0.7	32.0	4.7	158	0.1	0.8	1.7	46	3.00
Reference Materials																					
STD DS7	Standard		23.4	118.2	87.7	437	0.9	61.9	10.5	690	2.55	53.5	6.7	71.9	5.9	90	6.4	7.1	5.7	89	1.06
STD DS7	Standard		23.2	118.4	84.0	439	0.9	59.5	9.9	675	2.54	53.2	6.3	73.6	5.9	94	6.5	7.6	5.8	88	1.06
STD DS7	Standard		23.0	123.1	78.2	413	1.0	58.2	10.2	626	2.37	55.0	5.5	76.1	4.8	81	7.5	7.0	5.3	80	0.98
STD DS7	Standard		22.2	114.6	65.7	405	0.9	56.6	9.4	594	2.32	53.0	5.1	70.9	4.9	81	6.9	6.7	5.1	80	0.98
STD DS7 Expected			20.9	109	70.6	411	0.9	56	9.7	627	2.39	48.2	4.9	70	4.4	69	6.4	5.9	4.5	86	0.93
BLK	Blank		<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01
BLK	Blank		<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01
Prep Wash																					
G1	Prep Blank	<0.01	0.3	2.6	3.3	51	<0.1	4.4	5.0	559	2.04	0.7	1.9	0.7	4.2	63	<0.1	<0.1	0.1	40	0.53
G1	Prep Blank	<0.01	0.2	3.7	2.9	50	<0.1	4.0	4.6	565	2.05	16.6	1.8	1.6	4.0	64	<0.1	<0.1	0.1	39	0.54

QUALITY CONTROL REPORT

SMI08001023.1

Method		1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte		P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
Unit		%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm
MDL		0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5
Pulp Duplicates																		
933395	Drill Core	0.055	4	3	0.53	236	0.002	2	1.05	0.024	0.58	<0.1	0.06	3.9	0.5	0.77	3	1.2
REP 933395	QC	0.055	4	4	0.54	232	0.003	1	1.05	0.027	0.60	<0.1	0.06	4.0	0.6	0.76	3	1.2
933492	Drill Core	0.061	6	11	0.60	42	0.013	1	1.18	0.055	0.21	0.1	0.03	5.1	0.2	2.60	4	2.0
REP 933492	QC	0.056	6	10	0.56	55	0.015	2	1.11	0.054	0.21	0.2	0.02	4.7	0.2	2.42	4	2.0
Core Reject Duplicates																		
933437	Drill Core	0.074	11	10	0.79	110	0.001	3	1.25	0.039	0.17	0.3	0.01	4.2	0.1	1.70	5	1.8
DUP 933437	QC	0.069	11	9	0.80	98	0.001	2	1.35	0.043	0.20	0.4	0.01	4.2	0.2	1.63	4	1.8
Reference Materials																		
STD DS7	Standard	0.081	16	202	1.10	408	0.130	45	1.08	0.093	0.48	4.5	0.21	2.6	4.7	0.21	5	4.0
STD DS7	Standard	0.083	16	196	1.12	415	0.138	51	1.11	0.093	0.48	4.4	0.22	2.6	4.5	0.21	5	4.4
STD DS7	Standard	0.072	15	195	1.04	398	0.122	38	1.01	0.080	0.44	4.2	0.20	2.8	4.2	0.18	5	4.1
STD DS7	Standard	0.077	15	168	1.03	371	0.118	40	1.03	0.085	0.42	4.0	0.19	2.5	4.2	0.18	6	3.8
STD DS7 Expected		0.08	13	163	1.05	370	0.124	39	0.959	0.073	0.44	3.8	0.2	2.5	4.2	0.21	4.6	3.5
BLK	Blank	<0.001	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
BLK	Blank	<0.001	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
Prep Wash																		
G1	Prep Blank	0.082	8	8	0.62	260	0.129	<1	1.02	0.067	0.53	<0.1	<0.01	2.1	0.4	<0.05	6	<0.5
G1	Prep Blank	0.076	9	9	0.61	262	0.116	1	1.02	0.069	0.49	<0.1	<0.01	2.1	0.4	<0.05	6	<0.5



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.

Vancouver BC V6C 1Z7 Canada

Submitted By:

Glen Garratt

Receiving Lab:

Canada-Smithers

Received:

October 06, 2008

Report Date:

October 21, 2008

Page:

1 of 2

CERTIFICATE OF ANALYSIS

SMI08001024.1

CLIENT JOB INFORMATION

Project: Zymo
Shipment ID: zy-co-08-12
P.O. Number
Number of Samples: 28

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
DISP-RJT Dispose of Reject After 90 days

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Mincord Exploration Consultants Ltd.
110 - 325 Howe St.
Vancouver BC V6C 1Z7
Canada

CC: Bob Johnston

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status
R150	27	Crush split and pulverize drill core to 200 mesh		
1DX15	28	1:1:1 Aqua Regia digestion ICP-MS analysis	15	Completed

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only. All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.

“**” asterisk indicates that an analytical result could not be provided due to unusually high levels of interference from other elements.



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
 Report Date: October 21, 2008

Page: 2 of 2 Part 1

CERTIFICATE OF ANALYSIS

SMI08001024.1

Method	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
Unit	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	
MDL	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	
933458	Drill Core	6.63	6.7	2478	13.0	105	3.5	6.9	15.8	392	5.01	10.3	0.4	141.5	2.2	79	0.5	1.9	1.1	81	2.23
933459	Drill Core	7.14	7.5	1692	10.5	82	0.8	8.5	16.9	454	5.07	4.1	0.5	104.8	2.8	56	0.4	0.4	0.5	129	1.47
933460	Drill Core	7.08	4.5	706.9	6.8	47	0.5	4.1	12.9	356	3.82	1.9	0.4	36.4	2.3	27	0.2	0.1	0.6	80	1.25
933461	Drill Core	6.53	4.9	1204	9.9	75	1.0	5.5	14.4	426	3.93	3.3	0.5	64.2	3.0	43	0.3	0.2	0.5	100	1.50
933462	Drill Core	8.09	7.4	1219	9.4	65	0.4	4.6	17.7	390	3.87	1.5	0.5	48.6	2.9	30	0.3	<0.1	0.4	92	1.41
933463	Drill Core	6.93	19.6	1069	9.8	68	0.9	4.7	13.4	394	3.43	3.7	0.8	38.2	3.6	33	0.4	0.2	0.6	54	1.77
933464	Drill Core	6.94	13.2	1158	9.2	63	0.8	6.8	18.1	503	4.27	3.0	0.4	49.9	2.0	38	0.2	0.1	0.6	78	2.08
933465	Drill Core	6.46	30.9	1112	12.9	54	0.5	8.9	20.3	418	4.61	2.8	0.5	48.7	1.2	40	0.3	0.1	0.6	74	1.69
933466	Drill Core	7.13	11.4	965.1	14.1	60	0.7	8.6	16.6	424	4.49	3.8	0.4	40.7	1.3	39	0.4	0.1	0.7	74	1.79
933467	Drill Core	5.06	8.1	2093	12.6	91	0.8	13.4	23.3	371	5.62	2.1	0.7	92.9	1.2	50	0.5	0.1	0.6	108	1.69
933468	Drill Core	6.83	6.6	942.5	7.9	61	0.4	10.7	17.4	437	4.66	1.7	0.4	35.1	0.9	91	0.3	0.1	0.5	106	2.12
933469	Drill Core	6.67	7.9	540.1	6.8	36	0.3	12.5	13.7	399	4.27	1.6	0.3	22.5	1.2	92	0.1	0.3	0.5	89	3.15
933500	Drill Core	11.90	21.1	603.6	6.1	26	0.5	10.9	13.4	268	4.61	26.1	0.5	33.5	1.3	55	<0.1	0.8	1.5	76	1.94
933501	Drill Core	7.20	9.9	435.8	6.9	32	0.3	13.5	14.6	248	4.68	1.3	0.3	26.3	1.2	63	<0.1	0.4	0.8	120	1.81
933502	Drill Core	7.64	5.1	264.0	6.3	30	0.2	10.2	11.5	274	4.49	0.8	0.2	13.6	1.1	74	0.2	<0.1	0.8	119	1.46
933503	Drill Core	7.43	8.7	317.1	6.7	30	0.3	12.2	13.4	223	4.54	1.1	0.3	19.6	1.1	67	<0.1	<0.1	0.9	126	1.35
933504	Drill Core	7.40	14.6	451.4	4.3	28	0.3	10.6	11.0	259	4.31	0.7	0.3	27.1	1.3	87	<0.1	<0.1	1.1	121	1.78
933505	Drill Core	7.75	17.5	192.6	4.4	29	0.2	9.8	10.0	447	4.15	5.1	0.3	15.5	1.5	115	<0.1	0.1	0.4	114	2.14
933506	Drill Core	7.15	14.0	340.4	6.0	26	0.2	10.9	14.8	243	4.03	2.8	0.2	25.1	1.3	64	<0.1	0.4	0.7	79	2.02
933507	Drill Core	7.25	21.4	275.9	5.3	27	0.2	12.6	7.1	223	3.29	1.2	0.6	26.4	1.4	91	<0.1	0.2	0.6	114	1.57
933508	Drill Core	7.25	59.8	311.2	9.3	26	0.2	11.4	11.3	188	3.92	<0.5	0.3	18.1	1.4	57	<0.1	0.2	0.8	88	1.53
933509	Drill Core	7.35	54.7	982.1	4.9	33	0.6	10.4	17.6	328	5.59	1.1	0.7	113.8	2.7	278	<0.1	0.4	2.4	127	3.24
933510	Rock Pulp	0.04	8.5	3254	17.0	133	0.6	136.6	15.3	871	6.04	12.8	0.3	248.9	1.8	207	0.6	9.9	0.6	58	2.94
933511	Drill Core	7.11	15.5	361.7	3.6	77	0.2	11.8	22.3	460	5.59	35.5	0.8	21.6	2.6	293	0.5	8.1	0.5	147	4.03
933512	Drill Core	7.21	36.6	741.4	18.6	57	1.0	5.4	13.0	340	3.72	2.0	1.0	35.3	2.1	89	0.4	0.9	0.9	61	2.35
933513	Drill Core	7.39	28.7	190.3	3.0	23	0.1	4.7	5.1	231	2.87	<0.5	0.5	15.8	2.3	127	<0.1	0.3	0.6	56	2.11
933514	Drill Core	8.17	20.4	254.7	16.9	49	0.3	3.8	5.6	339	3.04	4.2	0.5	20.9	2.3	103	0.4	0.7	0.6	35	2.87
933515	Drill Core	7.14	17.6	212.0	22.6	36	0.3	3.1	4.9	285	2.85	2.3	0.7	16.2	2.4	104	0.3	0.4	0.6	43	2.46



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Mincord Exploration Consultants Ltd.**

110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo

Report Date: October 21, 2008

Page: 2 of 2 Part 2

CERTIFICATE OF ANALYSIS

SMI08001024.1

Method Analyte Unit MDL	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
	P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se	
	%	ppm	ppm	%	ppm	%	ppm	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm		
	0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.01	0.05	1	1	0.5
933458	Drill Core	0.159	15	15	0.93	34	0.030	4	1.79	0.066	0.19	0.1	0.03	4.7	0.2	2.21	8	1.6
933459	Drill Core	0.072	8	21	1.20	33	0.238	2	2.19	0.188	0.38	0.3	0.02	9.1	0.3	1.92	10	2.2
933460	Drill Core	0.088	7	13	0.78	22	0.167	3	1.56	0.069	0.14	0.2	<0.01	4.7	0.1	1.24	7	1.7
933461	Drill Core	0.075	9	13	1.00	32	0.223	3	2.04	0.131	0.20	0.4	0.02	6.5	0.2	1.24	9	1.5
933462	Drill Core	0.085	7	10	0.97	20	0.184	3	1.80	0.078	0.13	0.4	0.01	5.2	<0.1	1.41	9	1.4
933463	Drill Core	0.066	12	7	0.65	31	0.072	3	1.48	0.088	0.25	0.4	0.01	2.9	0.2	1.31	7	1.6
933464	Drill Core	0.067	7	15	0.93	17	0.094	2	1.80	0.087	0.20	0.3	0.01	5.8	0.2	1.73	7	2.3
933465	Drill Core	0.056	6	21	0.66	23	0.148	3	1.78	0.121	0.25	0.6	0.02	6.8	0.3	2.40	7	3.8
933466	Drill Core	0.076	6	18	0.60	20	0.121	2	1.74	0.106	0.17	0.3	0.01	6.1	0.2	2.11	6	2.3
933467	Drill Core	0.093	7	27	0.60	27	0.239	3	2.39	0.162	0.19	0.5	0.02	9.0	0.2	2.74	9	2.5
933468	Drill Core	0.085	7	21	0.89	34	0.161	2	2.53	0.244	0.28	0.2	<0.01	8.6	0.3	1.96	8	2.1
933469	Drill Core	0.060	7	20	0.81	72	0.092	4	2.31	0.194	0.38	0.3	0.01	8.1	0.4	1.93	7	2.3
933500	Drill Core	0.052	5	19	0.77	41	0.097	1	1.84	0.138	0.33	<0.1	<0.01	7.4	0.5	3.21	6	1.9
933501	Drill Core	0.054	5	25	0.94	37	0.211	2	2.65	0.247	0.28	0.2	<0.01	11.0	0.4	2.52	9	1.4
933502	Drill Core	0.064	4	25	1.02	38	0.202	1	2.49	0.240	0.33	<0.1	<0.01	11.4	0.5	2.00	9	1.5
933503	Drill Core	0.060	4	26	0.98	48	0.210	2	2.37	0.255	0.31	0.2	<0.01	11.9	0.5	2.52	9	1.2
933504	Drill Core	0.064	4	27	1.12	68	0.239	3	2.91	0.319	0.57	<0.1	<0.01	12.2	0.9	1.87	10	1.6
933505	Drill Core	0.126	7	22	1.15	78	0.212	2	3.36	0.394	0.63	<0.1	<0.01	11.5	0.9	1.61	10	1.0
933506	Drill Core	0.057	8	21	0.89	31	0.095	2	2.06	0.194	0.24	<0.1	<0.01	6.9	0.3	2.57	7	1.6
933507	Drill Core	0.046	5	29	1.08	52	0.202	2	2.53	0.323	0.37	0.2	<0.01	10.6	0.5	1.53	8	0.9
933508	Drill Core	0.044	4	25	1.08	22	0.117	2	1.81	0.184	0.18	0.3	<0.01	8.0	0.3	2.93	7	1.1
933509	Drill Core	0.104	12	20	1.65	37	0.149	2	3.32	0.306	0.58	0.2	0.01	9.9	0.8	3.95	11	2.2
933510	Rock Pulp	0.116	6	193	1.18	38	0.002	5	1.24	0.058	0.41	0.5	1.37	6.5	0.2	3.01	3	9.7
933511	Drill Core	0.146	11	16	1.83	67	0.188	3	3.43	0.281	0.63	0.2	0.03	9.3	0.7	2.91	9	1.7
933512	Drill Core	0.165	10	10	0.90	45	0.085	3	2.20	0.230	0.32	0.3	0.01	4.9	0.4	2.65	7	1.7
933513	Drill Core	0.044	5	12	1.21	92	0.118	2	3.23	0.431	0.61	<0.1	<0.01	6.1	0.8	1.36	8	0.8
933514	Drill Core	0.050	7	6	0.90	72	0.031	4	2.27	0.232	0.44	0.1	<0.01	3.5	0.5	2.05	6	1.4
933515	Drill Core	0.028	6	8	1.04	79	0.061	2	2.23	0.234	0.36	0.1	<0.01	4.2	0.5	1.76	7	0.9

QUALITY CONTROL REPORT

SMI08001024.1

Method	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
Unit	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	
MDL	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	
Core Reject Duplicates																					
933503	Drill Core	7.43	8.7	317.1	6.7	30	0.3	12.2	13.4	223	4.54	1.1	0.3	19.6	1.1	67	<0.1	<0.1	0.9	126	1.35
DUP 933503	QC		8.2	331.2	6.6	30	0.3	11.1	13.8	233	4.64	0.9	0.3	28.7	1.0	65	0.1	<0.1	0.9	129	1.35
Reference Materials																					
STD DS7	Standard		20.1	106.2	85.8	402	0.8	56.1	9.3	633	2.41	52.5	6.1	64.3	5.5	86	6.4	6.9	5.5	82	1.00
STD DS7	Standard		20.8	106.0	78.7	414	0.8	58.3	9.4	629	2.40	52.1	5.7	63.9	5.2	87	6.4	6.8	5.3	82	1.00
STD DS7 Expected			20.9	109	70.6	411	0.9	56	9.7	627	2.39	48.2	4.9	70	4.4	69	6.4	5.9	4.5	86	0.93
BLK	Blank		<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01
Prep Wash																					
G1	Prep Blank	<0.01	0.5	4.8	4.6	48	<0.1	3.6	4.8	599	2.15	1.2	2.3	1.1	4.9	87	<0.1	0.1	0.1	42	0.66
G1	Prep Blank	<0.01	0.6	3.3	4.0	47	<0.1	5.0	4.7	606	2.10	1.2	2.4	<0.5	5.1	81	<0.1	<0.1	0.1	42	0.64

QUALITY CONTROL REPORT

SMI08001024.1

Method		1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte		P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se
Unit		%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm
MDL		0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5
Core Reject Duplicates																		
933503	Drill Core	0.060	4	26	0.98	48	0.210	2	2.37	0.255	0.31	0.2	<0.01	11.9	0.5	2.52	9	1.2
DUP 933503	QC	0.066	4	24	1.01	44	0.211	2	2.40	0.240	0.33	0.3	<0.01	12.0	0.5	2.57	9	1.9
Reference Materials																		
STD DS7	Standard	0.077	15	177	1.03	397	0.122	42	1.02	0.085	0.45	4.2	0.20	2.4	4.6	0.19	5	3.7
STD DS7	Standard	0.079	14	175	1.03	379	0.123	40	1.02	0.084	0.44	3.9	0.21	2.4	4.5	0.19	5	3.6
STD DS7 Expected		0.08	13	163	1.05	370	0.124	39	0.959	0.073	0.44	3.8	0.2	2.5	4.2	0.21	4.6	3.5
BLK	Blank	<0.001	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5
Prep Wash																		
G1	Prep Blank	0.080	10	15	0.63	271	0.148	<1	1.18	0.116	0.60	<0.1	<0.01	2.3	0.4	<0.05	5	<0.5
G1	Prep Blank	0.078	10	14	0.62	265	0.144	3	1.12	0.103	0.60	<0.1	<0.01	2.2	0.4	<0.05	5	<0.5



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.

Vancouver BC V6C 1Z7 Canada

Submitted By:

Glen Garratt

Receiving Lab:

Canada-Smithers

Received:

October 06, 2008

Report Date:

October 22, 2008

Page:

1 of 3

CERTIFICATE OF ANALYSIS

SMI08001025.1

CLIENT JOB INFORMATION

Project: Zymo
Shipment ID: zy-co-08-13
P.O. Number
Number of Samples: 33

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
DISP-RJT Dispose of Reject After 90 days

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Mincord Exploration Consultants Ltd.
110 - 325 Howe St.
Vancouver BC V6C 1Z7
Canada

CC: Bob Johnston

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status
R150	32	Crush split and pulverize drill core to 200 mesh		
1DX15	33	1:1:1 Aqua Regia digestion ICP-MS analysis	15	Completed

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only. All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.

** asterisk indicates that an analytical result could not be provided due to unusually high levels of interference from other elements.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

ACME ANALYTICAL LABORATORIES LTD.

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.
Vancouver BC V6C 1Z7 Canada

Project:

Zymo

Report Date:

October 22, 2008

Page:

2 of 3

Part 1

CERTIFICATE OF ANALYSIS

SMI08001025.1

Method	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
Unit	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	
MDL	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	
933470	Drill Core	6.80	9.5	531.0	4.5	42	0.3	12.9	15.1	402	4.86	0.9	0.3	19.7	1.2	59	0.2	0.1	0.5	132	0.90
933471	Drill Core	5.44	4.0	837.3	4.7	40	0.4	12.1	18.6	372	6.13	1.2	0.3	27.3	1.0	50	0.1	<0.1	0.7	139	1.02
933472	Drill Core	7.22	6.2	1035	10.4	63	0.8	6.3	19.3	573	4.91	1.6	0.5	50.1	2.6	100	0.2	0.1	0.6	121	2.06
933473	Drill Core	6.52	6.6	713.8	5.8	46	0.5	5.6	14.1	546	4.38	12.6	0.2	20.5	0.6	123	0.2	9.6	0.3	80	3.55
933474	Drill Core	7.24	26.9	394.0	29.3	105	0.7	4.9	7.1	615	2.63	41.5	0.3	18.8	0.7	69	0.7	5.3	0.8	34	1.97
933475	Drill Core	6.39	7.4	976.8	6.7	49	0.9	7.9	13.4	394	4.13	4.3	0.3	37.8	1.2	65	0.2	1.6	0.5	82	1.81
933476	Drill Core	6.69	4.6	1608	5.0	57	1.3	6.3	20.5	393	6.66	2.3	0.6	97.1	2.0	93	0.4	<0.1	0.9	133	1.78
933477	Drill Core	7.45	4.0	1571	6.2	49	0.6	4.4	23.1	433	5.33	5.9	0.8	84.8	2.4	124	0.1	0.3	0.3	137	2.60
933478	Drill Core	5.50	4.8	797.8	7.0	43	0.5	10.2	18.2	328	4.58	1.7	0.4	27.8	1.4	52	0.2	0.3	0.4	85	1.35
933479	Drill Core	6.59	8.2	737.3	8.1	41	0.4	6.9	16.1	314	4.22	1.2	0.5	23.3	1.8	62	0.2	0.1	0.5	97	1.62
933480	Rock Pulp	0.04	7.5	3265	13.4	134	0.6	142.9	14.6	865	5.78	12.0	0.2	228.6	1.4	186	0.6	8.5	0.4	56	2.98
933481	Drill Core	6.79	12.5	1639	7.5	51	1.0	9.0	21.9	337	5.54	1.4	0.5	71.4	1.4	59	0.1	<0.1	0.8	96	1.61
933482	Drill Core	5.84	16.3	593.9	7.4	33	0.4	8.7	11.4	222	3.23	0.6	0.5	20.5	2.3	32	0.2	0.1	0.5	61	1.07
933483	Drill Core	7.32	17.4	434.2	7.4	44	0.3	9.1	10.6	222	3.21	0.7	0.4	15.1	2.3	59	0.2	0.3	0.5	59	1.30
933484	Drill Core	6.89	14.1	687.5	6.0	35	0.6	11.2	13.8	281	3.75	5.8	0.8	40.3	2.8	89	<0.1	1.8	1.0	39	2.34
933485	Drill Core	7.58	15.1	1039	56.1	127	2.4	12.2	12.6	592	3.58	337.4	1.9	43.9	1.9	104	0.8	5.1	2.0	23	2.92
933486	Drill Core	6.18	10.6	526.8	8.2	36	0.4	10.7	11.2	302	3.68	5.6	1.1	23.5	4.1	62	0.2	0.3	0.5	68	1.83
933487	Drill Core	6.88	38.9	466.3	9.4	31	0.3	11.2	9.5	229	3.26	8.7	0.5	34.3	2.5	49	0.2	1.0	0.4	54	1.91
933516	Drill Core	7.33	43.9	478.6	9.9	33	0.4	11.1	13.4	270	4.89	1.9	0.2	23.2	0.6	60	0.2	0.5	0.9	111	2.00
933517	Drill Core	7.54	37.8	342.7	5.0	29	0.2	11.1	12.3	215	4.43	1.7	0.4	18.6	0.9	73	<0.1	0.4	0.6	102	2.33
933518	Drill Core	7.70	16.2	234.2	5.1	29	0.2	10.1	9.4	219	4.16	0.5	0.2	13.3	1.1	75	<0.1	0.2	0.5	106	1.68
933519	Drill Core	8.72	24.0	283.5	10.2	29	0.3	11.1	11.8	350	3.61	4.8	0.4	18.1	1.1	63	0.2	0.4	0.5	71	2.49
933520	Drill Core	7.69	12.9	212.1	5.9	31	0.1	9.8	9.8	227	3.27	1.1	0.3	18.1	1.5	54	<0.1	0.2	0.3	78	1.82
933521	Drill Core	7.91	87.4	361.1	5.4	29	0.2	10.1	12.9	237	4.21	1.8	5.0	26.5	3.5	74	0.1	0.2	0.5	98	2.06
933522	Drill Core	7.76	7.2	231.8	5.4	28	0.2	12.8	12.5	213	3.57	2.1	0.2	19.2	1.3	43	0.1	0.2	0.4	89	1.56
933523	Drill Core	7.90	22.1	244.6	8.7	31	0.2	12.6	12.8	236	4.13	2.8	0.2	28.6	1.3	57	0.2	0.3	0.6	102	1.89
933524	Drill Core	8.16	12.2	142.2	12.9	37	0.2	13.6	11.4	233	3.93	1.9	0.3	22.1	1.5	53	0.2	0.2	0.5	98	1.62
933525	Drill Core	7.57	12.9	235.5	7.9	27	0.2	13.3	11.3	193	3.61	3.9	0.4	20.6	1.7	52	0.1	<0.1	0.7	93	1.70
933526	Drill Core	7.26	25.1	104.8	4.2	25	<0.1	11.1	10.0	263	4.23	1.5	0.3	12.5	1.3	45	<0.1	0.1	0.5	102	1.47
933527	Drill Core	7.00	17.6	175.0	7.2	37	0.2	12.6	16.4	301	4.82	3.8	0.3	19.7	1.0	77	0.1	0.4	0.5	110	2.07



ACME ANALYTICAL LABORATORIES LTD.
 1020 Cordova St. East Vancouver BC V6A 4A3 Canada
 Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Mincord Exploration Consultants Ltd.
 110 - 325 Howe St.
 Vancouver BC V6C 1Z7 Canada

Project: Zymo
Report Date: October 22, 2008

Page: 2 of 3 **Part** 2

CERTIFICATE OF ANALYSIS

SMI08001025.1

Method	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se	
Unit	%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
MDL	0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5	
933470	Drill Core	0.057	4	26	1.02	48	0.249	1	2.18	0.200	0.45	0.6	0.01	12.9	0.4	1.99	8	2.4
933471	Drill Core	0.071	4	29	1.11	43	0.257	1	2.21	0.153	0.33	0.5	<0.01	12.7	0.4	2.75	9	3.2
933472	Drill Core	0.087	6	12	1.25	40	0.193	1	2.69	0.195	0.29	0.4	<0.01	8.1	0.3	1.83	8	1.5
933473	Drill Core	0.130	8	10	0.80	99	0.084	2	2.11	0.167	0.21	0.4	<0.01	7.2	0.2	1.84	8	2.6
933474	Drill Core	0.058	6	6	0.57	101	0.016	2	1.35	0.105	0.24	0.2	0.01	4.7	0.3	1.11	4	1.4
933475	Drill Core	0.065	5	15	0.91	77	0.117	1	1.84	0.122	0.20	0.3	<0.01	8.3	0.3	1.80	7	1.9
933476	Drill Core	0.130	7	10	1.30	74	0.209	2	2.70	0.171	0.33	0.4	0.02	6.9	0.3	2.07	11	1.9
933477	Drill Core	0.118	9	5	1.16	73	0.164	3	2.59	0.167	0.25	0.2	0.02	4.2	0.2	1.68	9	1.2
933478	Drill Core	0.060	5	19	0.82	43	0.144	1	1.88	0.135	0.21	0.5	0.03	7.7	0.2	2.40	7	1.8
933479	Drill Core	0.091	6	14	0.96	34	0.186	2	2.24	0.112	0.13	0.7	0.02	5.5	<0.1	1.95	7	1.8
933480	Rock Pulp	0.117	6	180	1.21	47	0.002	5	1.00	0.055	0.33	0.6	1.27	6.5	0.2	2.98	3	8.8
933481	Drill Core	0.121	5	17	0.95	29	0.155	1	2.32	0.118	0.15	1.2	<0.01	6.2	0.1	2.82	8	2.2
933482	Drill Core	0.054	4	19	0.69	21	0.112	1	1.63	0.109	0.15	0.8	0.02	5.1	0.1	1.98	5	1.5
933483	Drill Core	0.034	5	17	0.65	44	0.092	1	1.82	0.163	0.15	0.8	0.01	4.7	0.2	1.97	5	1.3
933484	Drill Core	0.076	8	11	0.55	43	0.007	3	1.00	0.077	0.18	0.1	<0.01	4.6	0.2	2.09	3	1.2
933485	Drill Core	0.052	5	7	0.37	53	0.002	4	0.74	0.039	0.29	0.1	0.01	3.9	0.2	2.18	2	2.4
933486	Drill Core	0.069	9	17	0.75	86	0.053	2	1.39	0.074	0.16	0.4	<0.01	4.6	0.1	1.74	6	1.3
933487	Drill Core	0.049	7	15	0.53	64	0.008	3	1.32	0.093	0.28	0.2	0.01	4.0	0.3	1.90	5	1.5
933516	Drill Core	0.067	4	20	1.18	25	0.136	1	2.52	0.241	0.26	0.5	0.01	10.1	0.3	3.66	9	2.2
933517	Drill Core	0.190	7	23	1.06	38	0.111	2	2.50	0.257	0.28	0.4	<0.01	9.1	0.4	3.06	9	2.2
933518	Drill Core	0.062	3	21	1.19	37	0.161	1	2.76	0.307	0.35	0.3	<0.01	9.6	0.5	2.57	9	1.3
933519	Drill Core	0.048	6	16	0.78	36	0.021	2	1.91	0.184	0.27	0.2	<0.01	6.2	0.4	2.62	6	1.3
933520	Drill Core	0.048	4	17	0.84	70	0.087	1	1.81	0.151	0.17	0.3	0.02	7.3	0.2	1.70	6	1.0
933521	Drill Core	0.080	9	14	0.93	70	0.118	2	2.22	0.197	0.35	0.2	0.02	7.2	0.5	2.60	8	1.9
933522	Drill Core	0.050	3	21	0.76	23	0.102	1	2.00	0.160	0.19	0.2	<0.01	7.0	0.3	1.80	7	1.1
933523	Drill Core	0.064	4	20	0.80	31	0.101	2	2.29	0.216	0.26	0.4	0.02	8.0	0.5	2.32	8	1.4
933524	Drill Core	0.058	3	24	0.79	27	0.151	<1	2.09	0.121	0.22	0.6	<0.01	9.1	0.1	1.99	8	1.2
933525	Drill Core	0.063	4	20	0.74	34	0.142	1	2.41	0.212	0.25	0.4	<0.01	8.1	0.4	2.09	9	1.7
933526	Drill Core	0.062	3	15	1.00	39	0.206	2	2.78	0.179	0.26	0.3	0.01	9.4	0.3	1.44	10	0.7
933527	Drill Core	0.066	5	18	1.02	53	0.164	2	3.26	0.283	0.37	0.2	0.01	9.7	0.5	2.06	11	1.2



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.

Vancouver BC V6C 1Z7 Canada

Project:

Zymo

Report Date:

October 22, 2008

Page:

3 of 3

Part 1

CERTIFICATE OF ANALYSIS

SMI08001025.1

Method	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
Unit	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	
MDL	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	
933528	Drill Core	6.26	16.4	342.3	8.8	37	0.3	10.1	19.7	223	5.00	3.5	0.2	28.0	0.8	71	0.2	0.4	0.9	92	2.30
933529	Drill Core	7.53	5.2	92.0	50.2	90	0.5	7.4	5.7	799	3.33	27.9	0.2	19.0	1.2	85	0.5	1.4	0.3	78	2.00
933530	Drill Core	6.78	22.6	164.0	115.4	83	0.6	11.8	10.4	453	4.33	8.3	0.2	53.6	1.1	63	0.6	5.2	1.8	79	2.02



ACME ANALYTICAL LABORATORIES LTD.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Mincord Exploration Consultants Ltd.

110 - 325 Howe St.

Vancouver BC V6C 1Z7 Canada

Project:

Zymo

Report Date:

October 22, 2008

Page:

3 of 3

Part 2

CERTIFICATE OF ANALYSIS

SMI08001025.1

Method	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15
Analyte	P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se	
Unit	%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
MDL	0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5	
933528	Drill Core	0.076	3	16	1.08	31	0.126	1	2.71	0.246	0.27	0.2	<0.01	7.7	0.4	3.83	9	3.4
933529	Drill Core	0.052	4	15	1.07	67	0.123	2	2.81	0.286	0.28	0.2	0.02	7.2	0.4	1.30	9	1.0
933530	Drill Core	0.056	7	17	0.86	15	0.019	2	1.94	0.098	0.17	<0.1	0.63	5.9	0.4	2.41	8	1.4

QUALITY CONTROL REPORT


SMI08001025.1

Method	WGHT	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	V	Ca	
Unit	kg	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	ppm	%	
MDL	0.01	0.1	0.1	0.1	1	0.1	0.1	0.1	1	0.01	0.5	0.1	0.5	0.1	1	0.1	0.1	0.1	2	0.01	
Pulp Duplicates																					
933470	Drill Core	6.80	9.5	531.0	4.5	42	0.3	12.9	15.1	402	4.86	0.9	0.3	19.7	1.2	59	0.2	0.1	0.5	132	0.90
REP 933470	QC		8.8	528.0	4.7	42	0.3	13.5	15.6	393	4.81	0.6	0.3	19.8	1.1	54	0.1	0.1	0.5	132	0.88
Core Reject Duplicates																					
933482	Drill Core	5.84	16.3	593.9	7.4	33	0.4	8.7	11.4	222	3.23	0.6	0.5	20.5	2.3	32	0.2	0.1	0.5	61	1.07
DUP 933482	QC		15.3	694.6	7.4	34	0.4	9.6	13.7	237	3.43	0.7	0.5	19.4	2.1	34	0.1	<0.1	0.5	62	1.17
Reference Materials																					
STD DS7	Standard		20.3	113.8	69.7	430	0.9	57.6	9.3	623	2.41	54.0	4.9	61.5	4.3	70	6.4	6.4	4.4	86	0.96
STD DS7	Standard		20.3	111.2	70.4	438	0.9	57.7	9.1	627	2.40	51.5	4.8	62.0	4.2	66	6.3	6.0	4.4	88	0.98
STD DS7	Standard		20.1	106.2	85.8	402	0.8	56.1	9.3	633	2.41	52.5	6.1	64.3	5.5	86	6.4	6.9	5.5	82	1.00
STD DS7	Standard		20.8	106.0	78.7	414	0.8	58.3	9.4	629	2.40	52.1	5.7	63.9	5.2	87	6.4	6.8	5.3	82	1.00
STD DS7	Standard		19.5	114.4	74.9	418	0.8	61.4	10.2	608	2.42	52.9	5.2	59.0	4.6	65	6.5	5.9	4.9	81	0.93
STD DS7	Standard		18.3	113.3	75.9	397	0.8	57.3	9.6	603	2.33	50.6	5.0	52.4	4.5	60	6.3	5.5	4.7	79	0.92
STD DS7 Expected			20.9	109	70.6	411	0.9	56	9.7	627	2.39	48.2	4.9	70	4.4	69	6.4	5.9	4.5	86	0.93
BLK	Blank		<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01
BLK	Blank		<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01
BLK	Blank		<0.1	<0.1	<0.1	<1	<0.1	<0.1	<0.1	<1	<0.01	<0.5	<0.1	<0.5	<0.1	<1	<0.1	<0.1	<0.1	<2	<0.01
Prep Wash																					
G1	Prep Blank	<0.01	0.1	2.1	3.2	46	<0.1	3.4	4.5	590	2.09	<0.5	2.1	<0.5	4.5	78	<0.1	<0.1	0.1	41	0.58
G1	Prep Blank	<0.01	0.3	3.2	3.1	51	<0.1	4.3	4.6	571	2.08	<0.5	2.0	<0.5	4.7	76	<0.1	<0.1	0.1	42	0.57

QUALITY CONTROL REPORT

SMI08001025.1

Method		1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	1DX15	
Analyte		P	La	Cr	Mg	Ba	Ti	B	Al	Na	K	W	Hg	Sc	Tl	S	Ga	Se	
Unit		%	ppm	ppm	%	ppm	%	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	
MDL		0.001	1	1	0.01	1	0.001	1	0.01	0.001	0.01	0.1	0.01	0.1	0.1	0.05	1	0.5	
Pulp Duplicates																			
933470	Drill Core	0.057	4	26	1.02	48	0.249	1	2.18	0.200	0.45	0.6	0.01	12.9	0.4	1.99	8	2.4	
REP 933470	QC	0.056	3	26	1.03	47	0.234	2	2.19	0.193	0.44	0.5	0.01	12.5	0.4	1.98	8	2.0	
Core Reject Duplicates																			
933482	Drill Core	0.054	4	19	0.69	21	0.112	1	1.63	0.109	0.15	0.8	0.02	5.1	0.1	1.98	5	1.5	
DUP 933482	QC	0.077	5	19	0.70	23	0.111	1	1.73	0.111	0.16	1.0	0.02	5.0	0.1	2.06	5	1.4	
Reference Materials																			
STD DS7	Standard	0.081	13	180	1.04	409	0.111	46	1.02	0.084	0.44	4.6	0.23	2.1	4.6	0.20	5	3.8	
STD DS7	Standard	0.080	12	171	1.06	374	0.110	41	1.01	0.081	0.43	4.4	0.21	2.1	4.6	0.21	5	4.0	
STD DS7	Standard	0.077	15	177	1.03	397	0.122	42	1.02	0.085	0.45	4.2	0.20	2.4	4.6	0.19	5	3.7	
STD DS7	Standard	0.079	14	175	1.03	379	0.123	40	1.02	0.084	0.44	3.9	0.21	2.4	4.5	0.19	5	3.6	
STD DS7	Standard	0.079	12	183	1.02	395	0.114	44	0.95	0.077	0.41	4.3	0.20	2.2	4.4	0.18	4	3.5	
STD DS7	Standard	0.078	11	174	1.00	366	0.112	43	0.91	0.071	0.40	4.0	0.17	2.1	4.2	0.18	4	2.8	
STD DS7 Expected		0.08	13	163	1.05	370	0.124	39	0.959	0.073	0.44	3.8	0.2	2.5	4.2	0.21	4.6	3.5	
BLK	Blank	<0.001	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5	
BLK	Blank	<0.001	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5	
BLK	Blank	<0.001	<1	<1	<0.01	<1	<0.001	<1	<0.01	<0.001	<0.01	<0.1	<0.01	<0.1	<0.1	<0.05	<1	<0.5	
Prep Wash																			
G1	Prep Blank	0.081	9	9	0.63	269	0.142	<1	1.08	0.076	0.60	<0.1	<0.01	2.1	0.4	<0.05	5	<0.5	
G1	Prep Blank	0.083	8	9	0.64	255	0.136	<1	1.08	0.071	0.59	<0.1	<0.01	2.2	0.4	<0.05	5	<0.5	

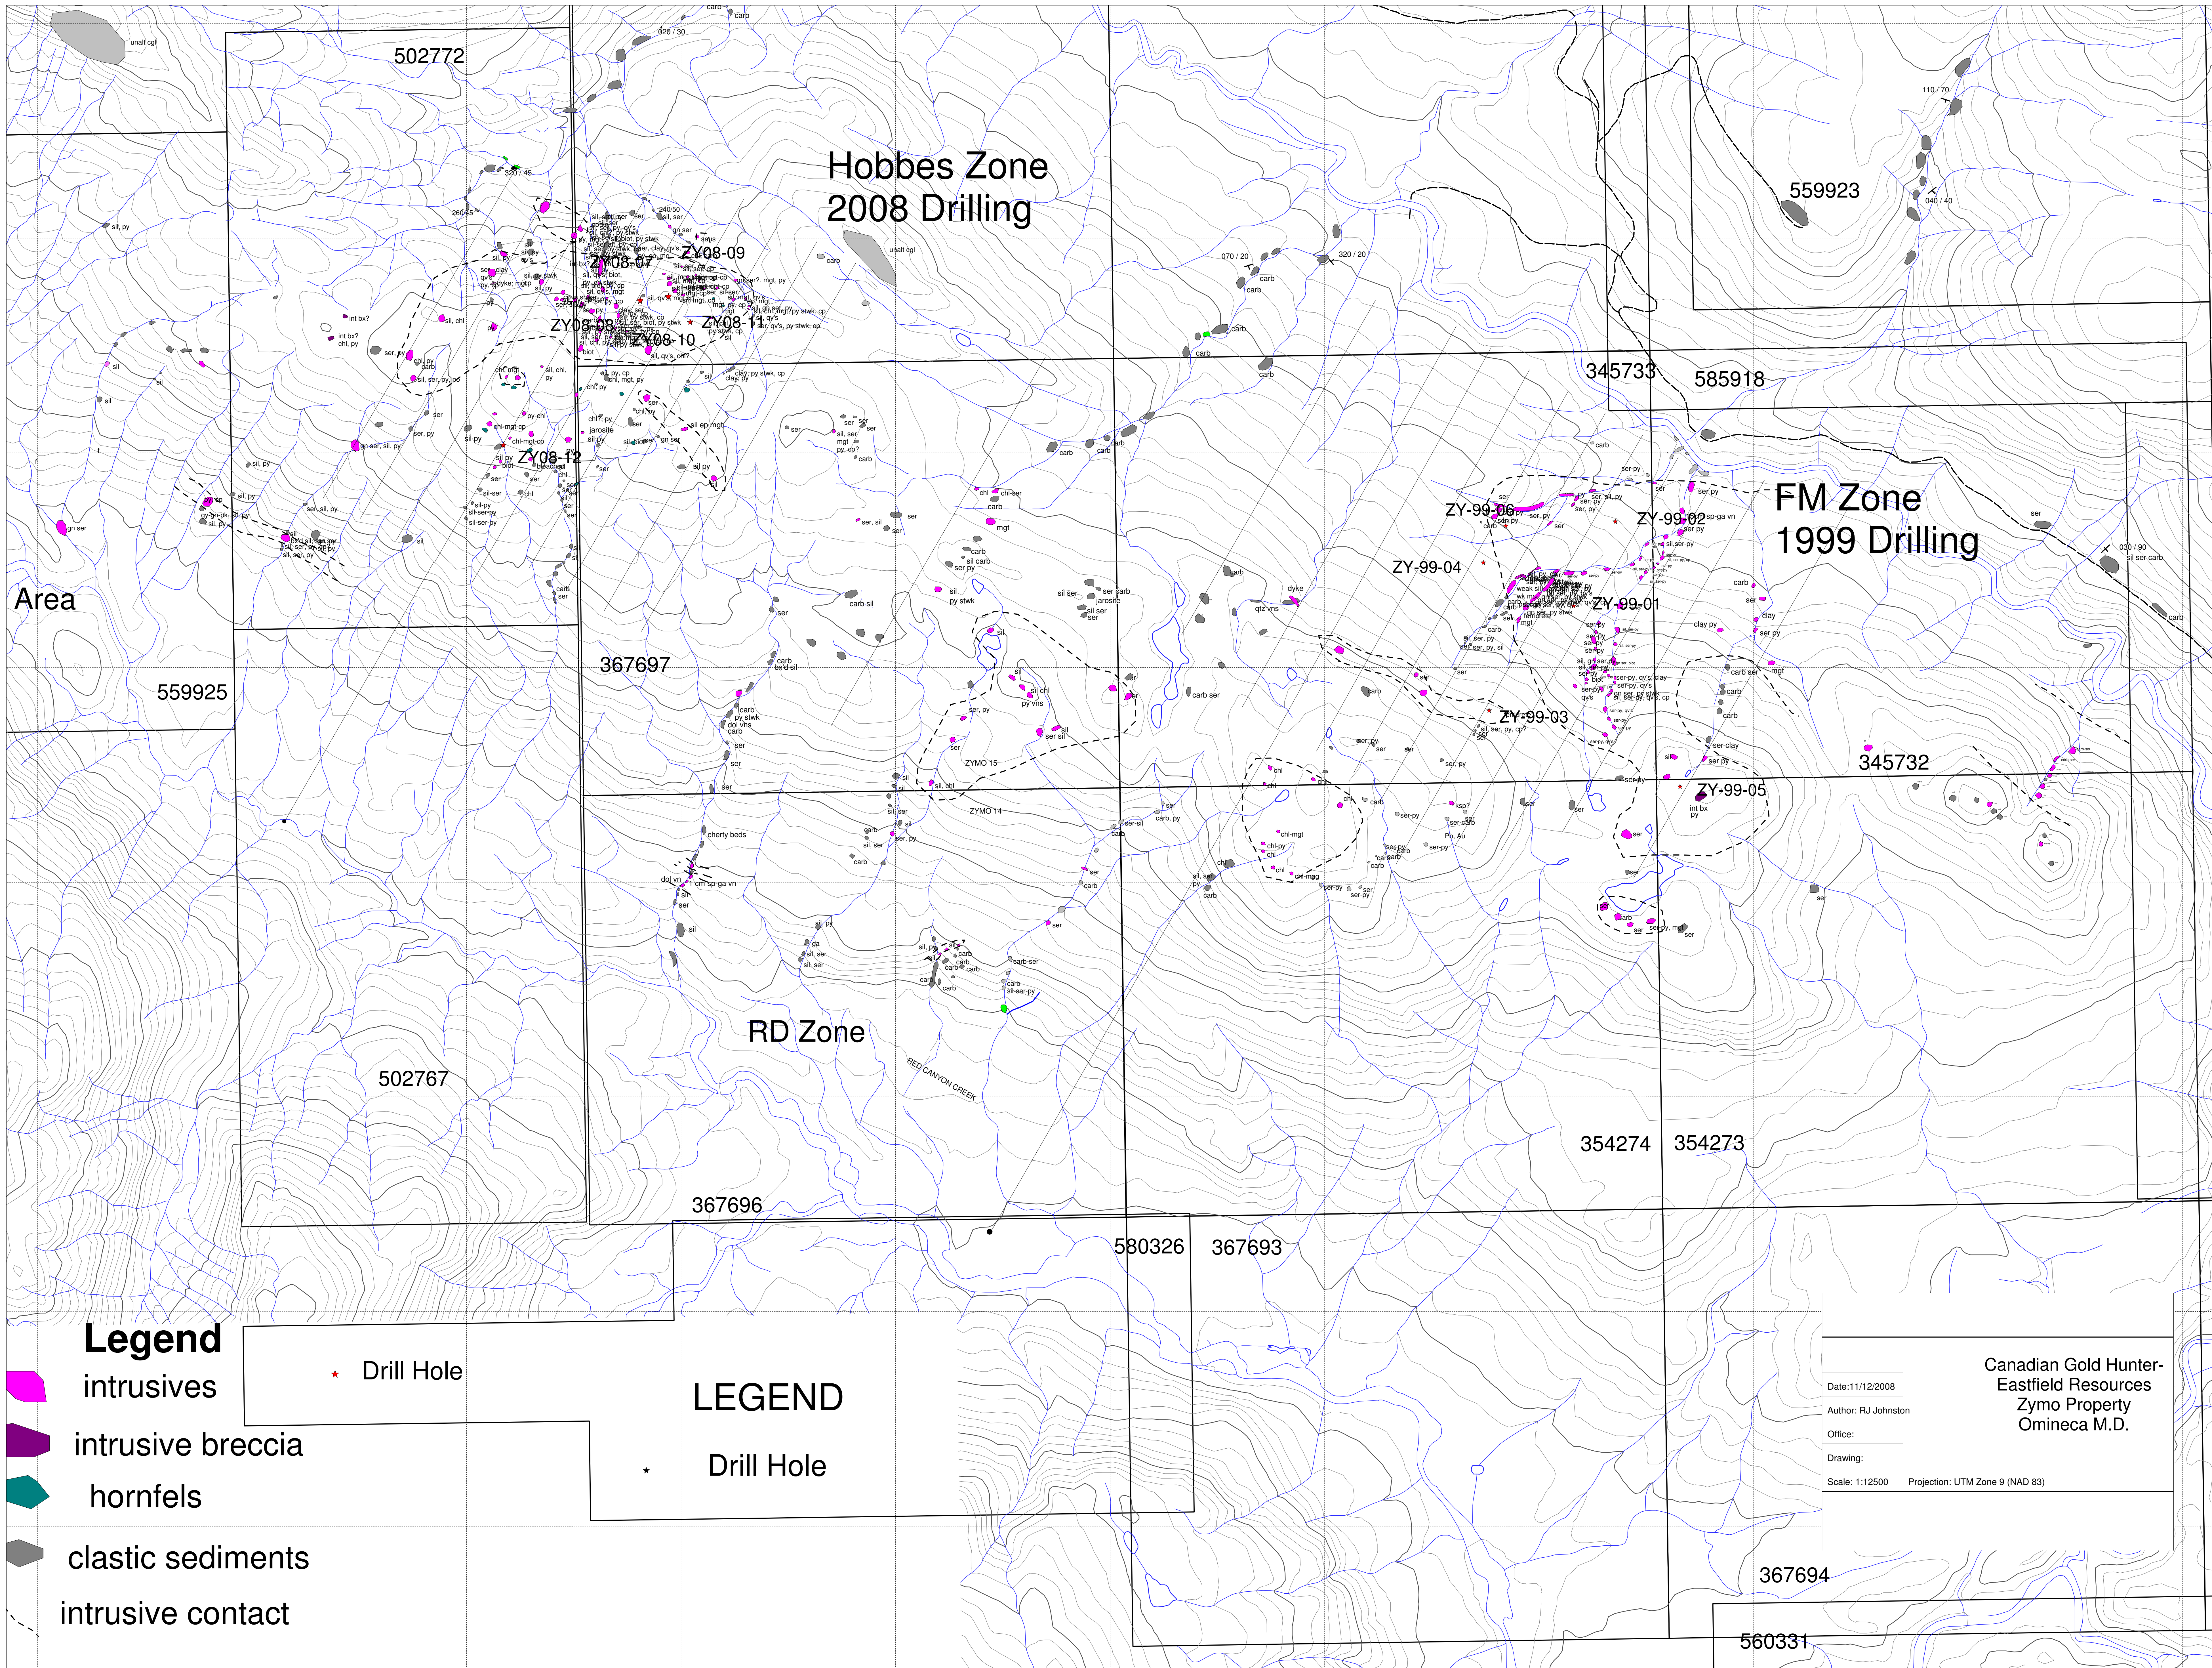






Area

Hobbes Zone
2008 Drilling

FM Zone
1999 Drilling

RD Zone

Legend

-  intrusives
-  intrusive breccia
-  hornfels
-  clastic sediments
-  intrusive contact

 Drill Hole

LEGEND

 Drill Hole

Date: 11/12/2008
 Author: RJ Johnston
 Office:
 Drawing:
 Scale: 1:12500

Projection: UTM Zone 9 (NAD 83)

Canadian Gold Hunter-
 Eastfield Resources
 Zymo Property
 Omineca M.D.

**ZYMO Property
Cu geochemistry
on 2008 chargeability
1:5000**

**Hobbes Zone
2008 Drilling**

**FM Zone
1999 Drilling**

URC Area

RD Zone

zymo_2008_final_soils by Cu

- 500 to 3,690 (32)
- 200 to 500 (61)
- 100 to 200 (156)
- 0 to 100 (909)

zymo_2008_final_rx by Cu

- 1,000 to 10,100 (27)
- 500 to 1,000 (14)
- 100 to 500 (124)
- 0 to 100 (315)

zymo_2007_soils_mod by Cu



- 500 to 4,020 (14)
- 200 to 500 (22)
- 100 to 200 (49)
- 0 to 100 (179)

old_zymo_soils_apr_29_08 by Cu_ppm

- 500 to 3,870 (4)
- 200 to 500 (19)
- 100 to 200 (34)
- 0 to 100 (276)

zymo_2007_rocks_mod by Cu

- 1,000 to 9,220 (19)
- 500 to 1,000 (7)
- 100 to 500 (22)
- 0 to 100 (110)

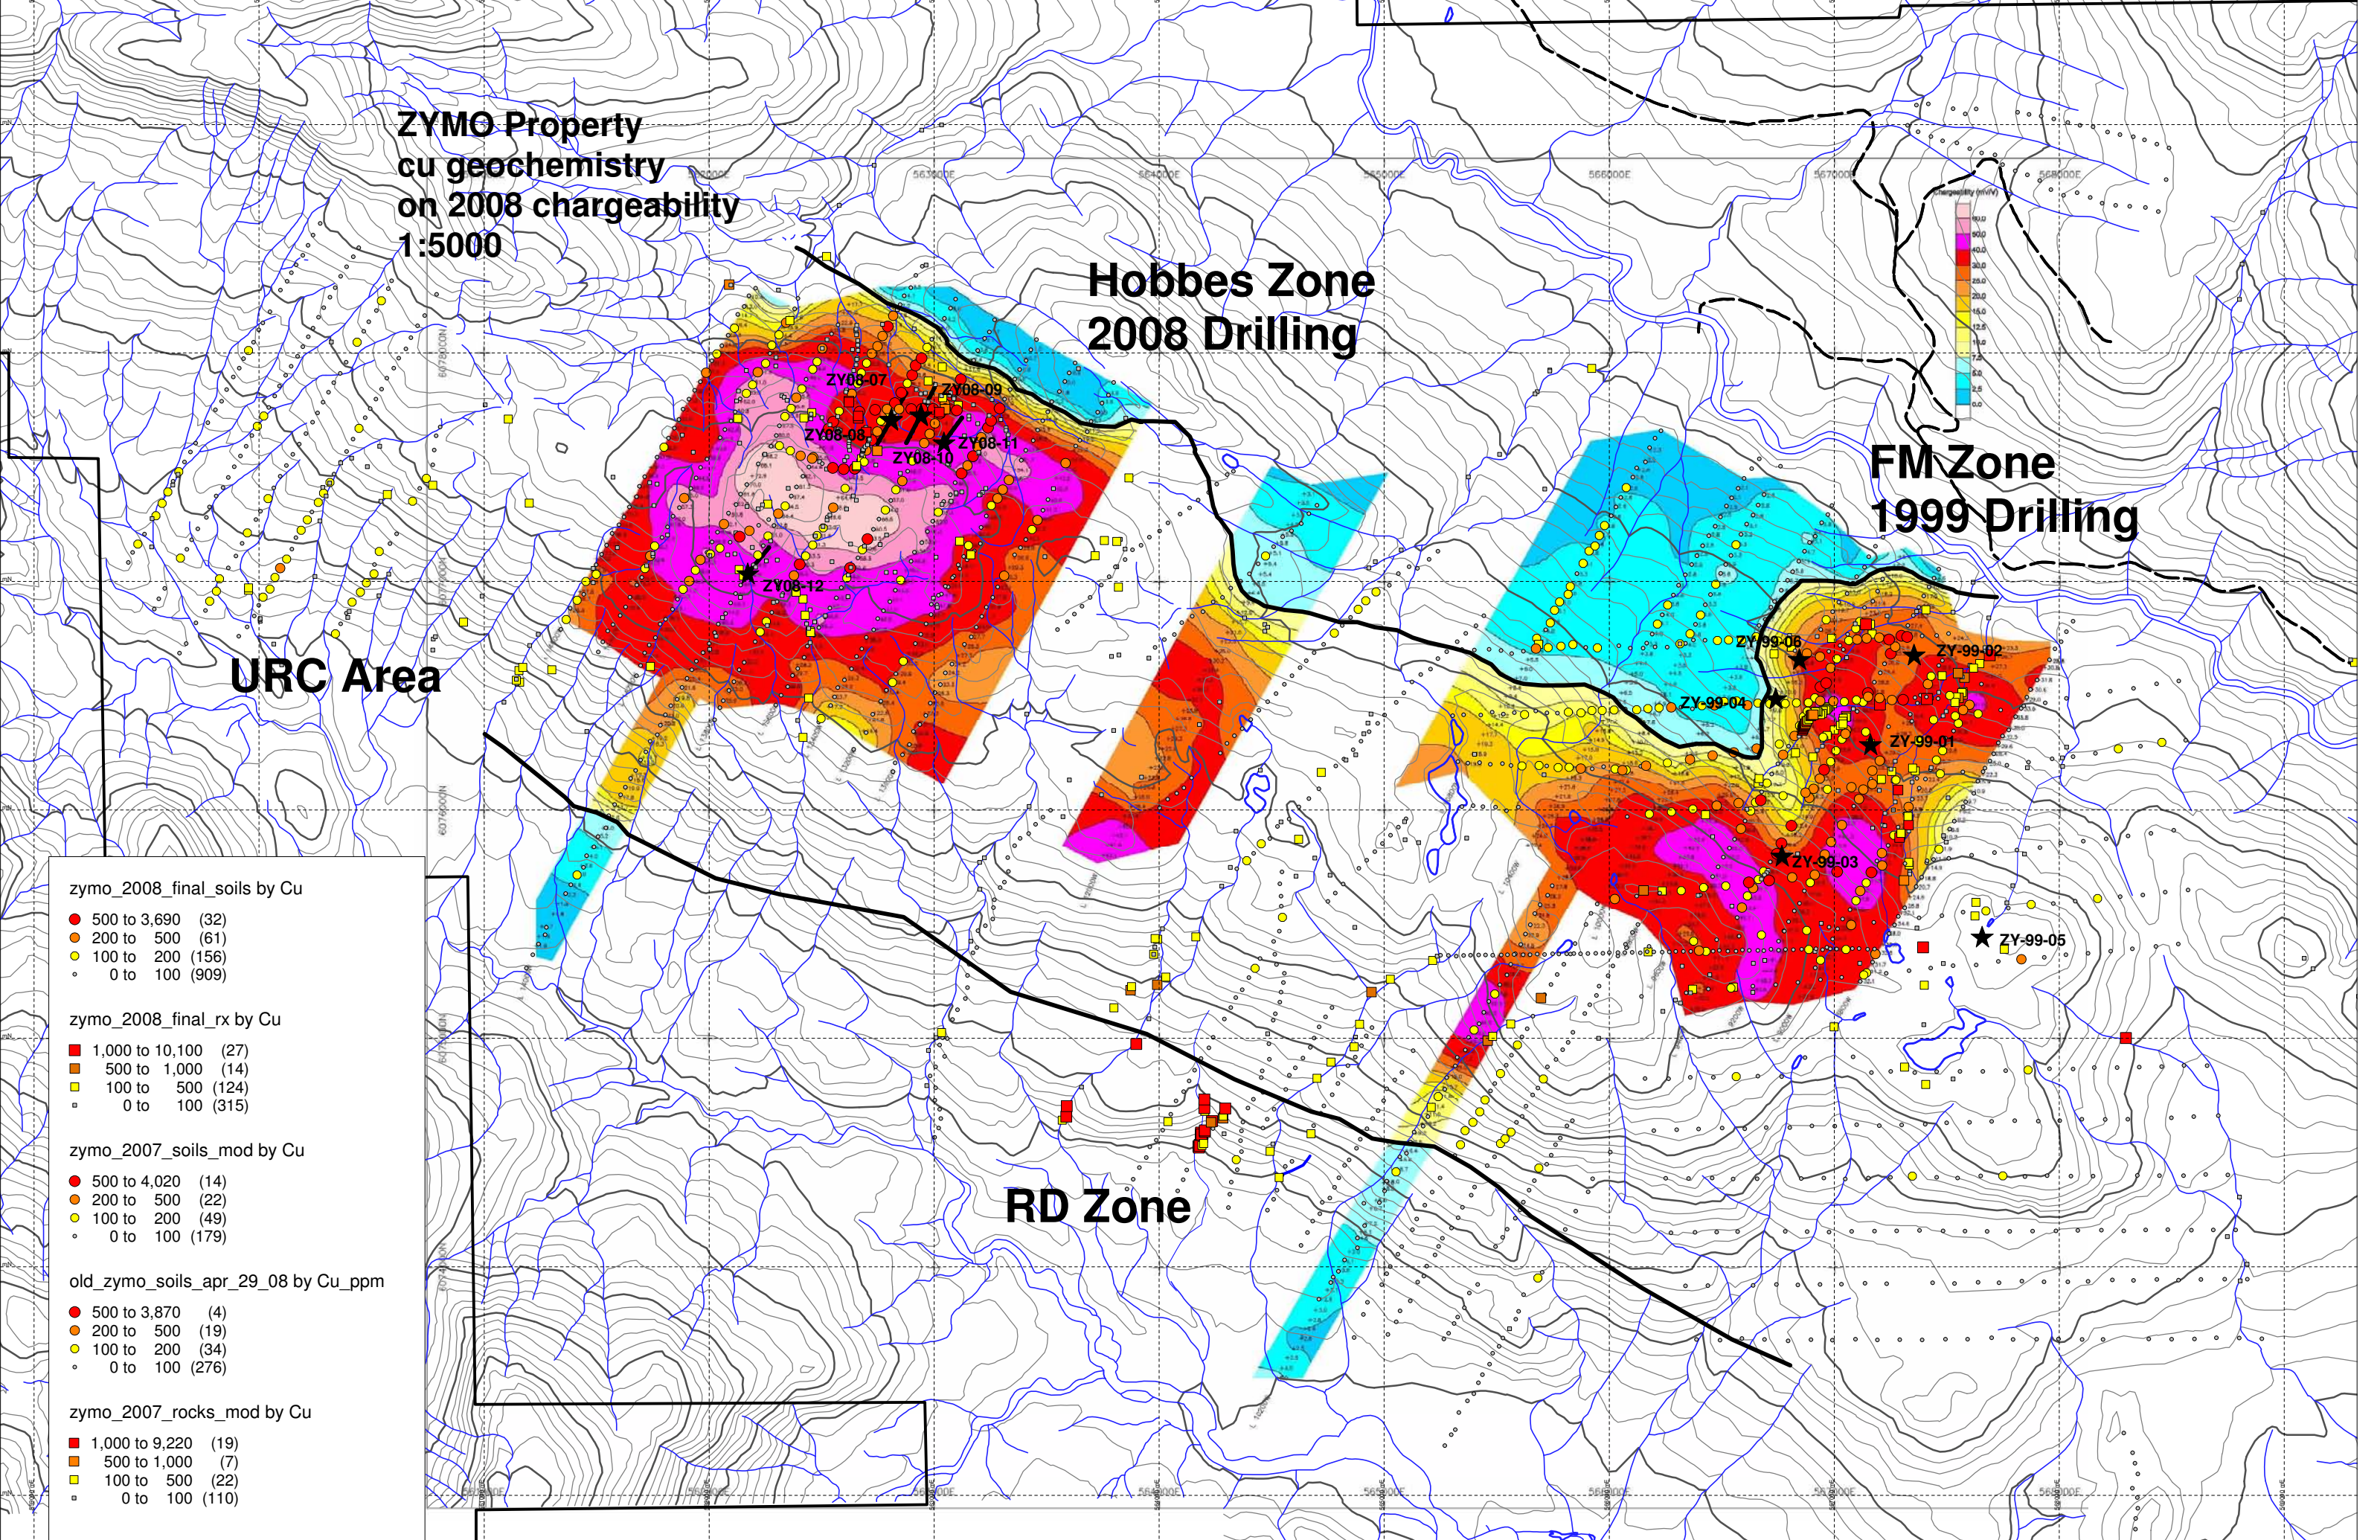

ZYMO Property
Cu geochemistry on airborne mag
1:5000

Hobbes Zone
2008 Drilling

FM Zone
1999 Drilling

URC Area

RD Zone

zymo_2008_final_soils by Cu

- 500 to 3,690 (32)
- 200 to 500 (61)
- 100 to 200 (156)
- 0 to 100 (909)

zymo_2008_final_rx by Cu

- 1,000 to 10,100 (27)
- 500 to 1,000 (14)
- 100 to 500 (124)
- 0 to 100 (315)

zymo_2007_soils_mod by Cu


- 500 to 4,020 (14)
- 200 to 500 (22)
- 100 to 200 (49)
- 0 to 100 (179)


old_zymo_soils_apr_29_08 by Cu_ppm

- 500 to 3,870 (4)
- 200 to 500 (19)
- 100 to 200 (34)
- 0 to 100 (276)

zymo_2007_rocks_mod by Cu

- 1,000 to 9,220 (19)
- 500 to 1,000 (7)
- 100 to 500 (22)
- 0 to 100 (110)

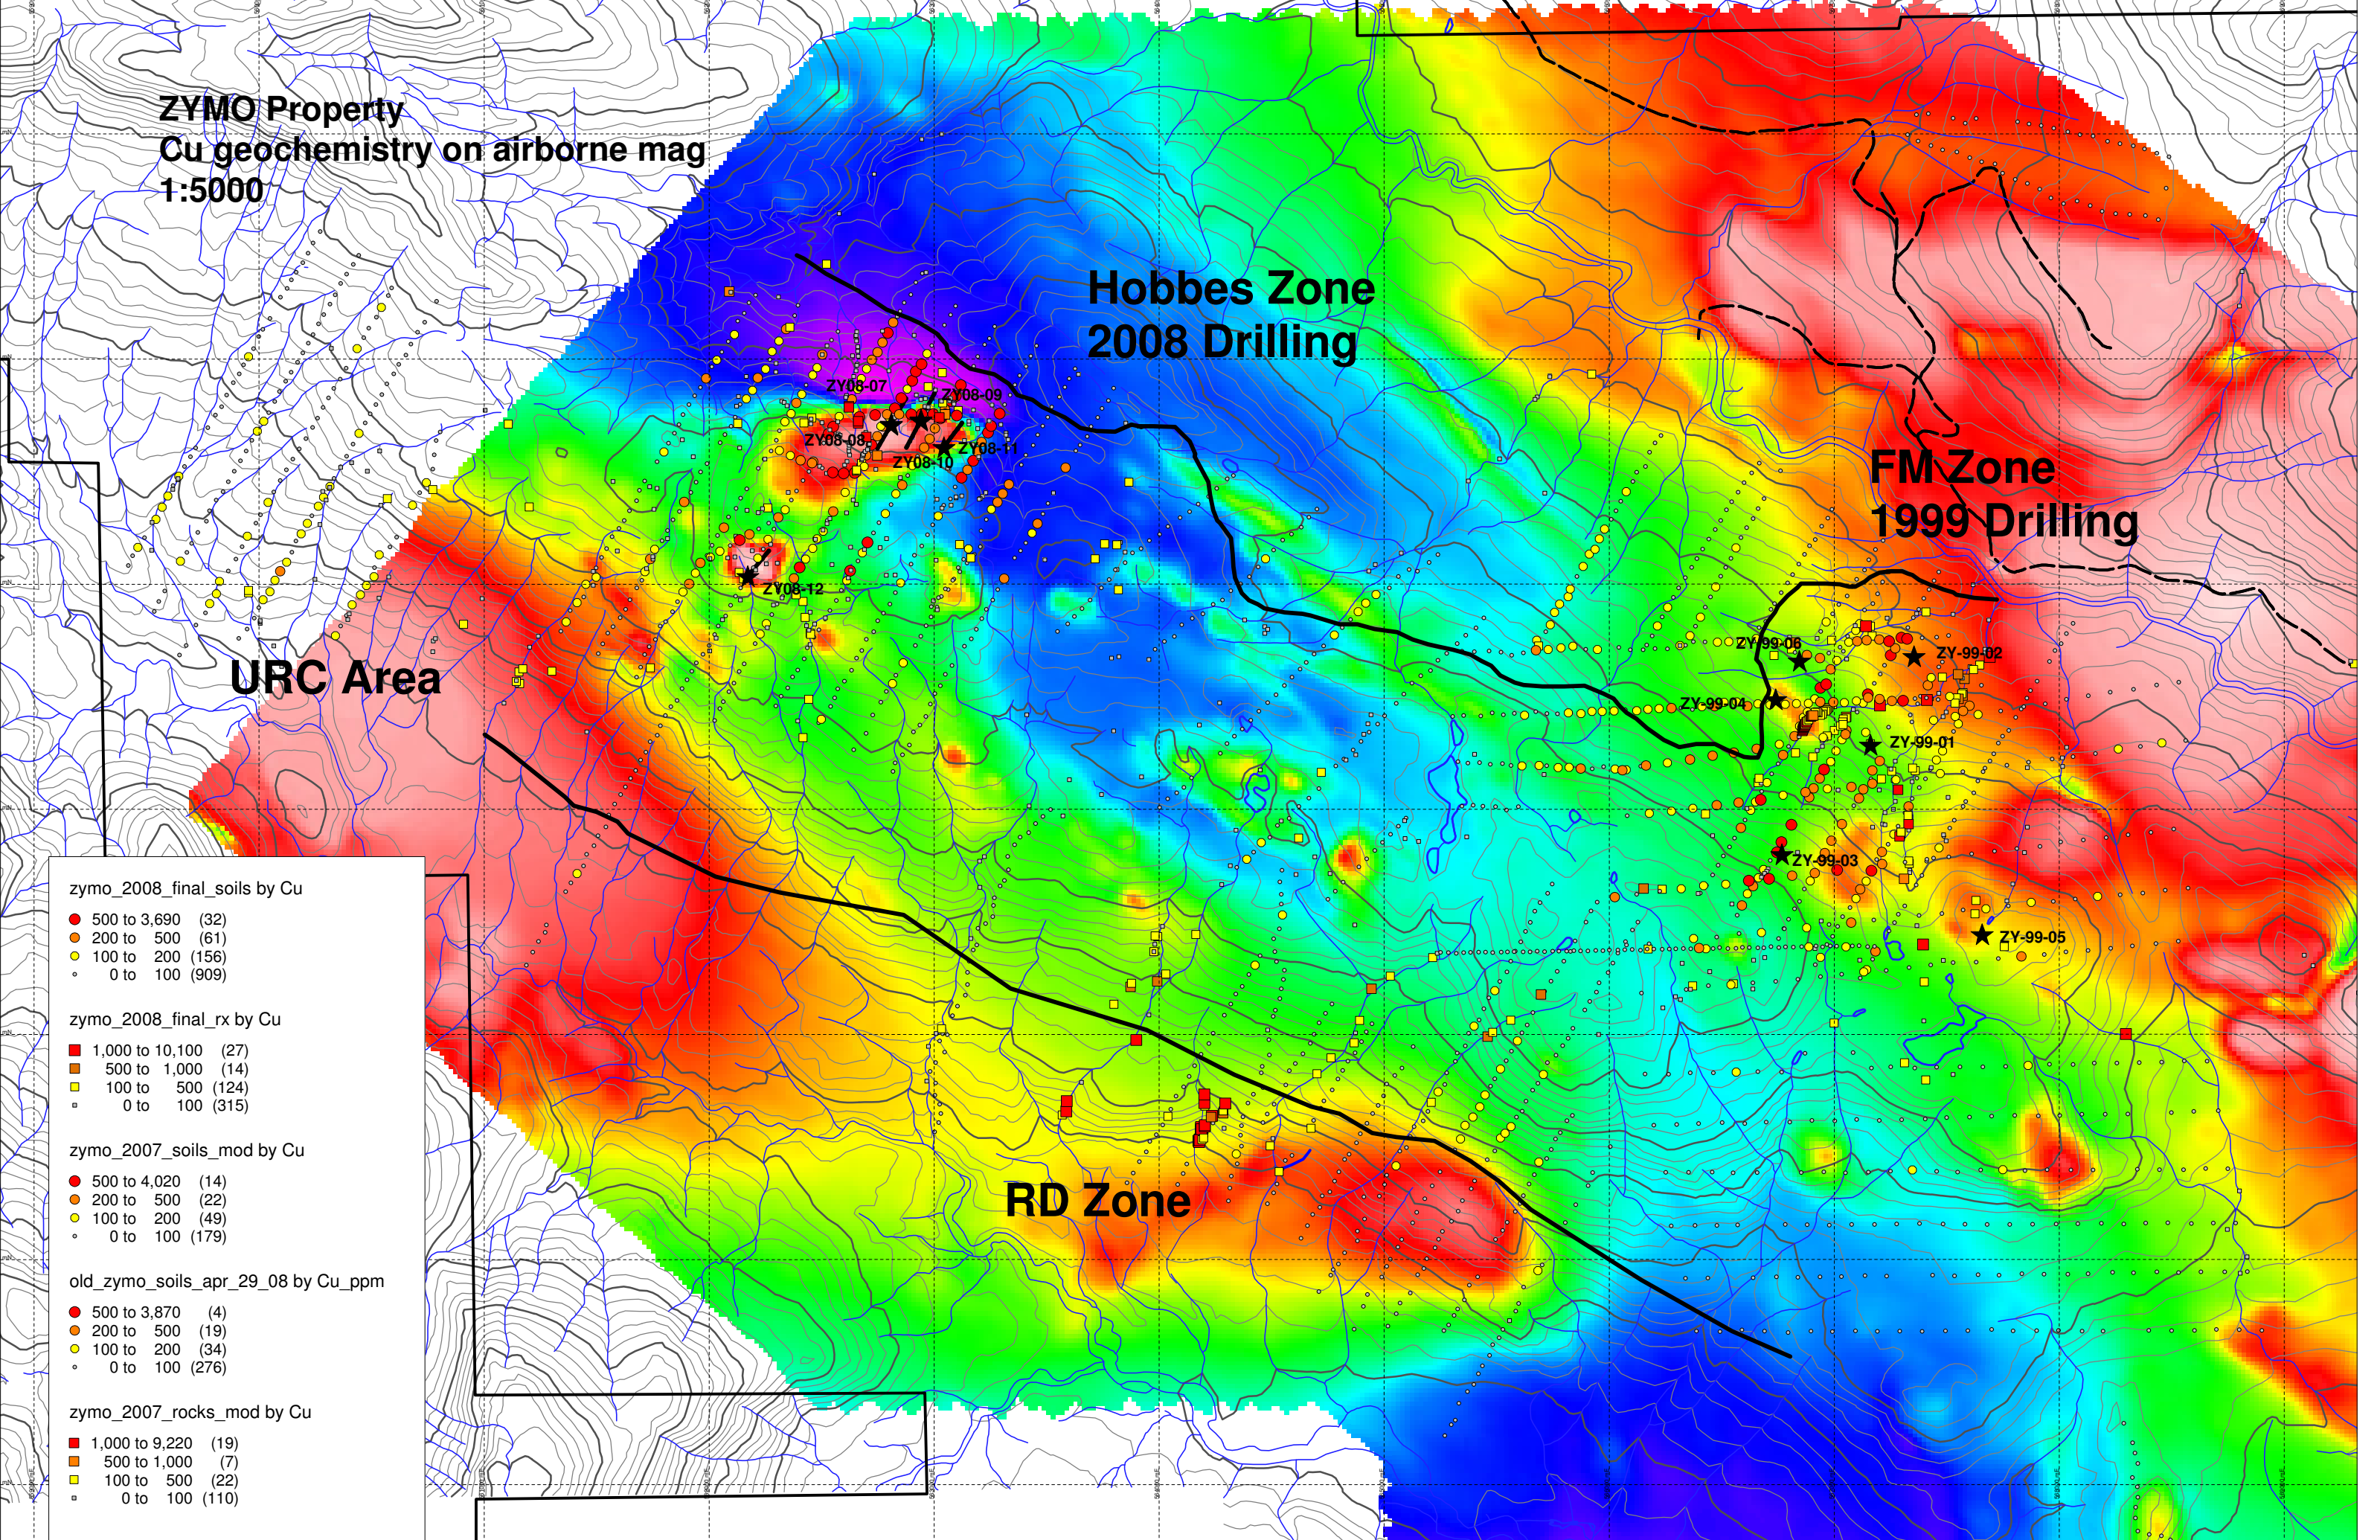


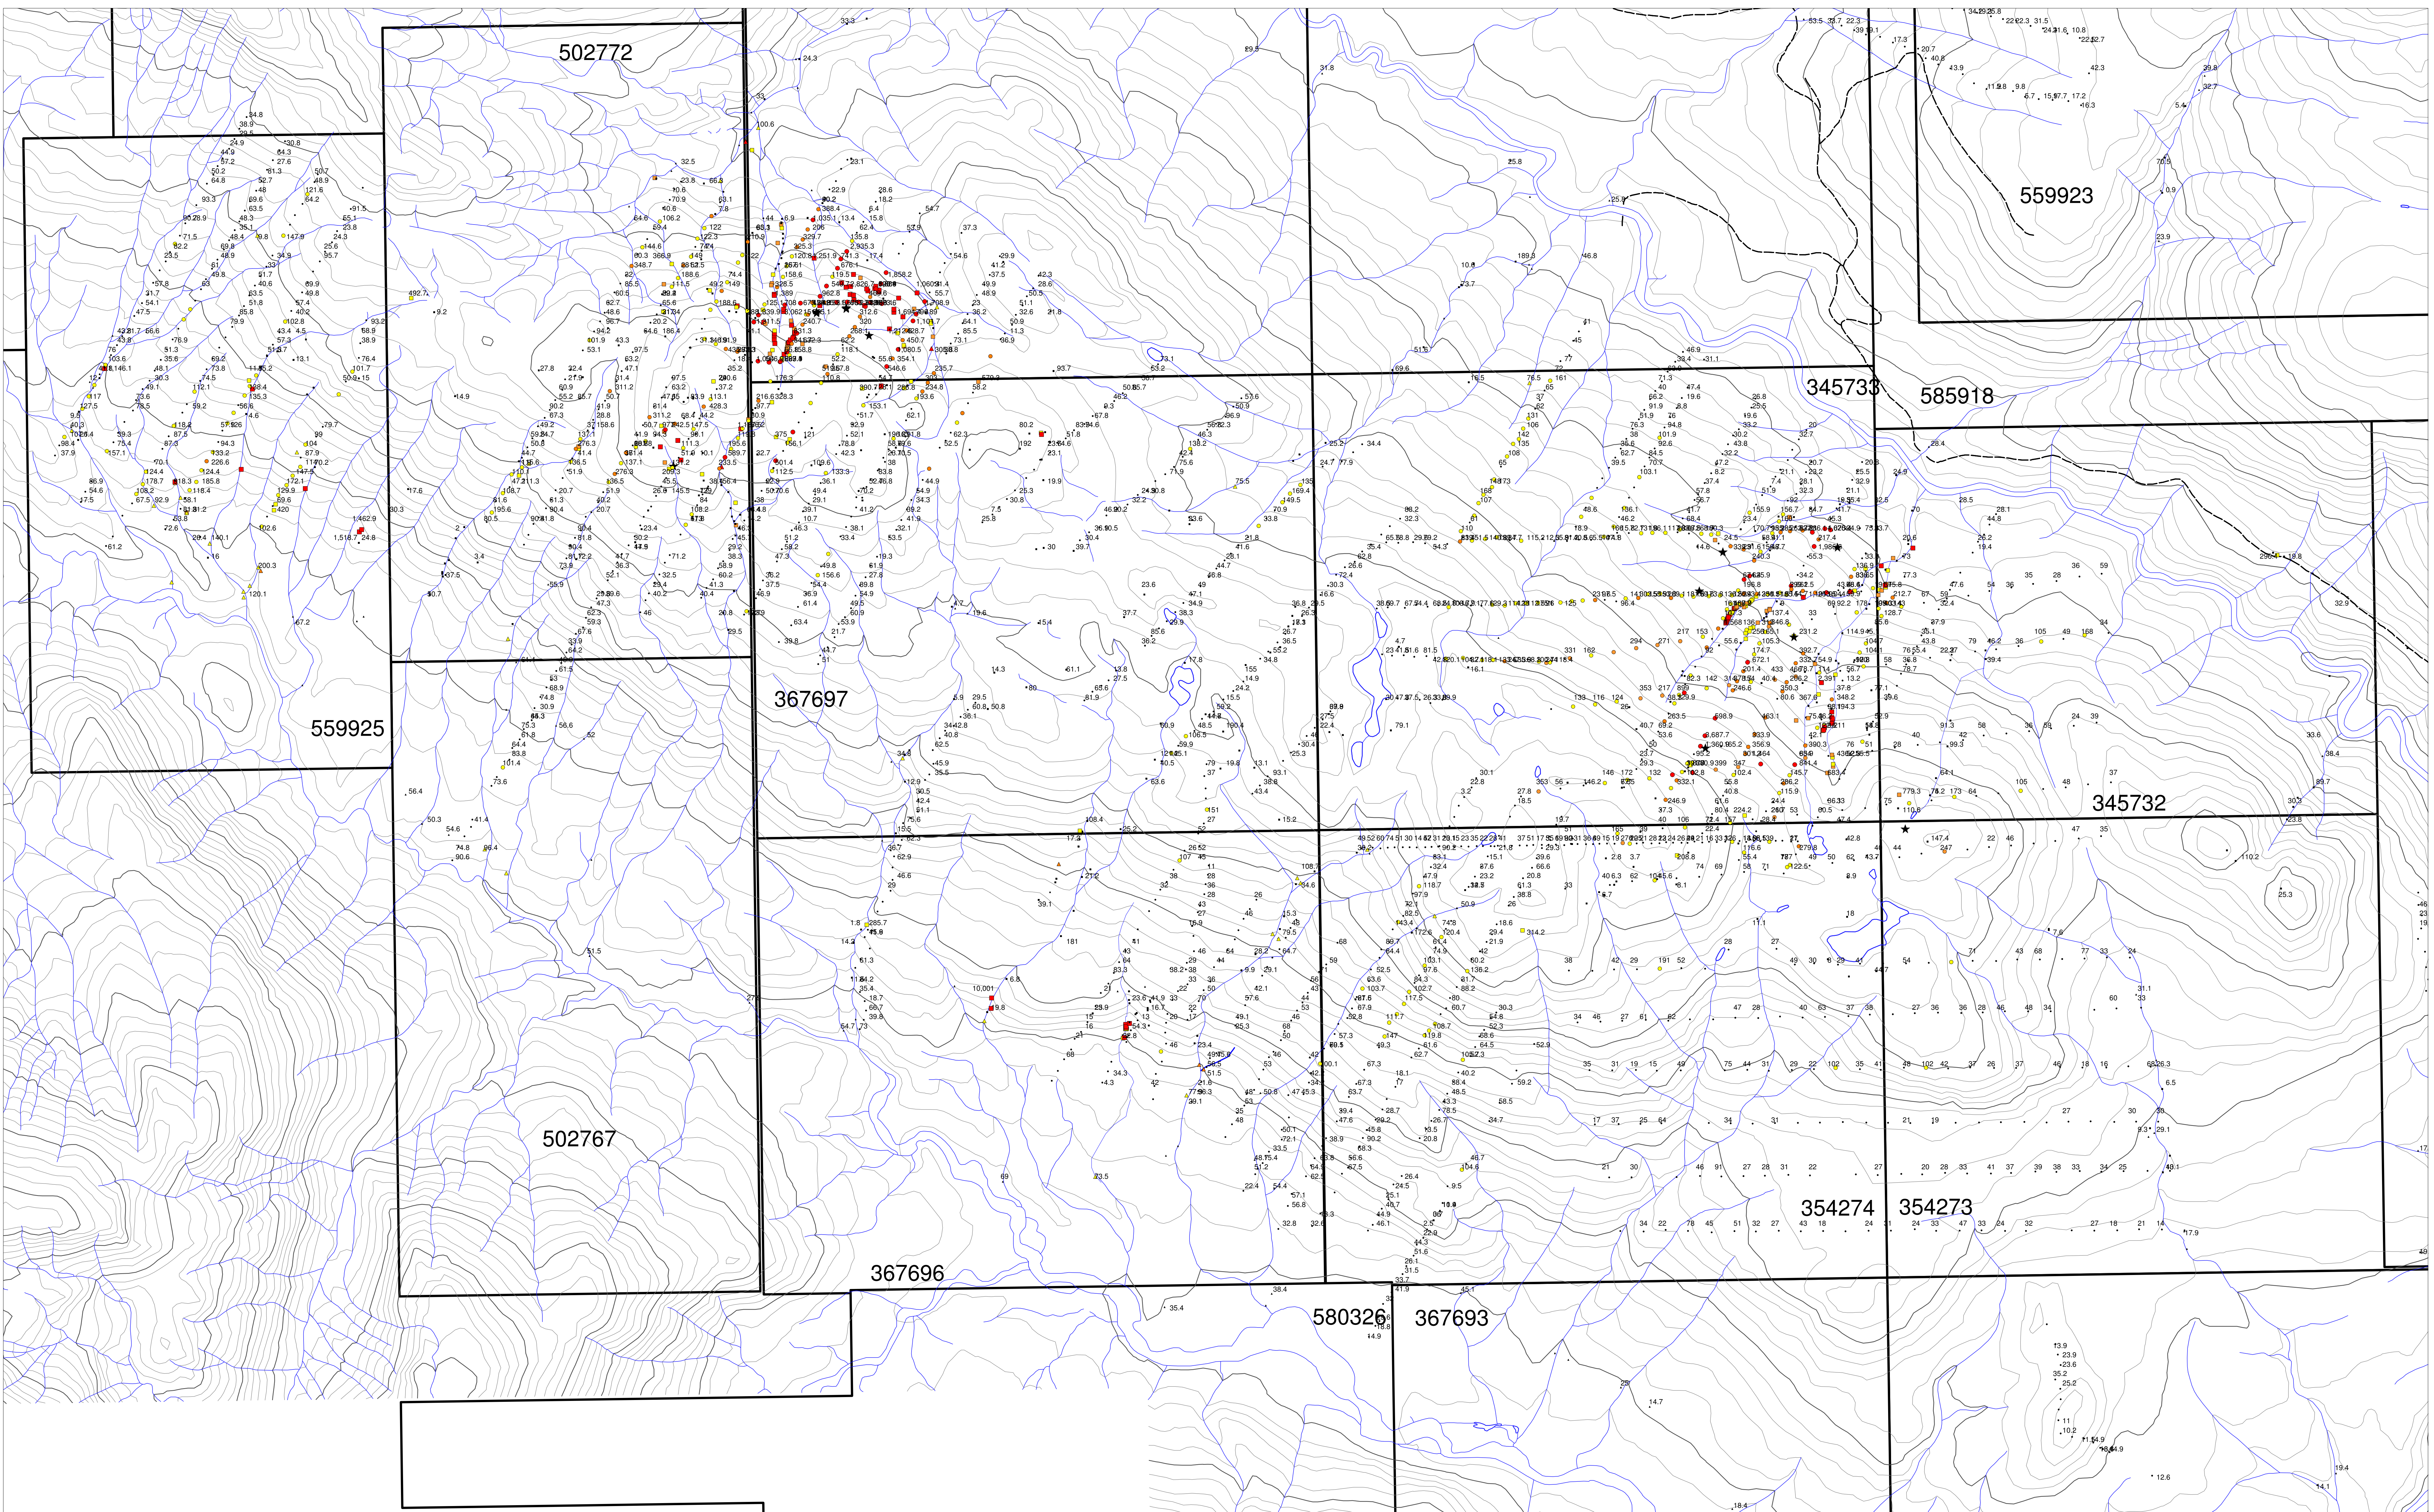


- old_zymo_soils_apr_29_08 by Cu.gpp
- 500 to 3.870 (4)
 - 300 to 500 (19)
 - 100 to 200 (34)
 - 0 to 100 (278)
- zymo_et_soils by Cu
- 500 to 4.000 (46)
 - 200 to 500 (83)
 - 100 to 200 (205)
 - 0 to 100 (1088)
- zymo_et_soils by Cu
- ▲ 250 to 472 (3)
 - ▲ 130 to 250 (5)
 - ▲ 70 to 150 (32)
 - ▲ 10 to 70 (147)
- zymo_et_rocks by Cu
- 1,000 to 10,100 (89)
 - 500 to 1,000 (60)
 - 200 to 500 (74)
 - 0 to 200 (393)


* Diamond Drill Hole

Date: 2/2/2009	Zymo Project Canadian Gold Hunter - Eastfield Resources Cu Geochemistry
Author: NJ	
Office:	
Drawing: 8	
Scale: 1:10000	Projection: UTM Zone 9 (NAD 83)

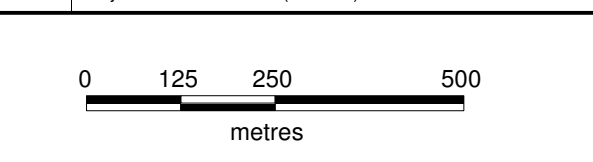


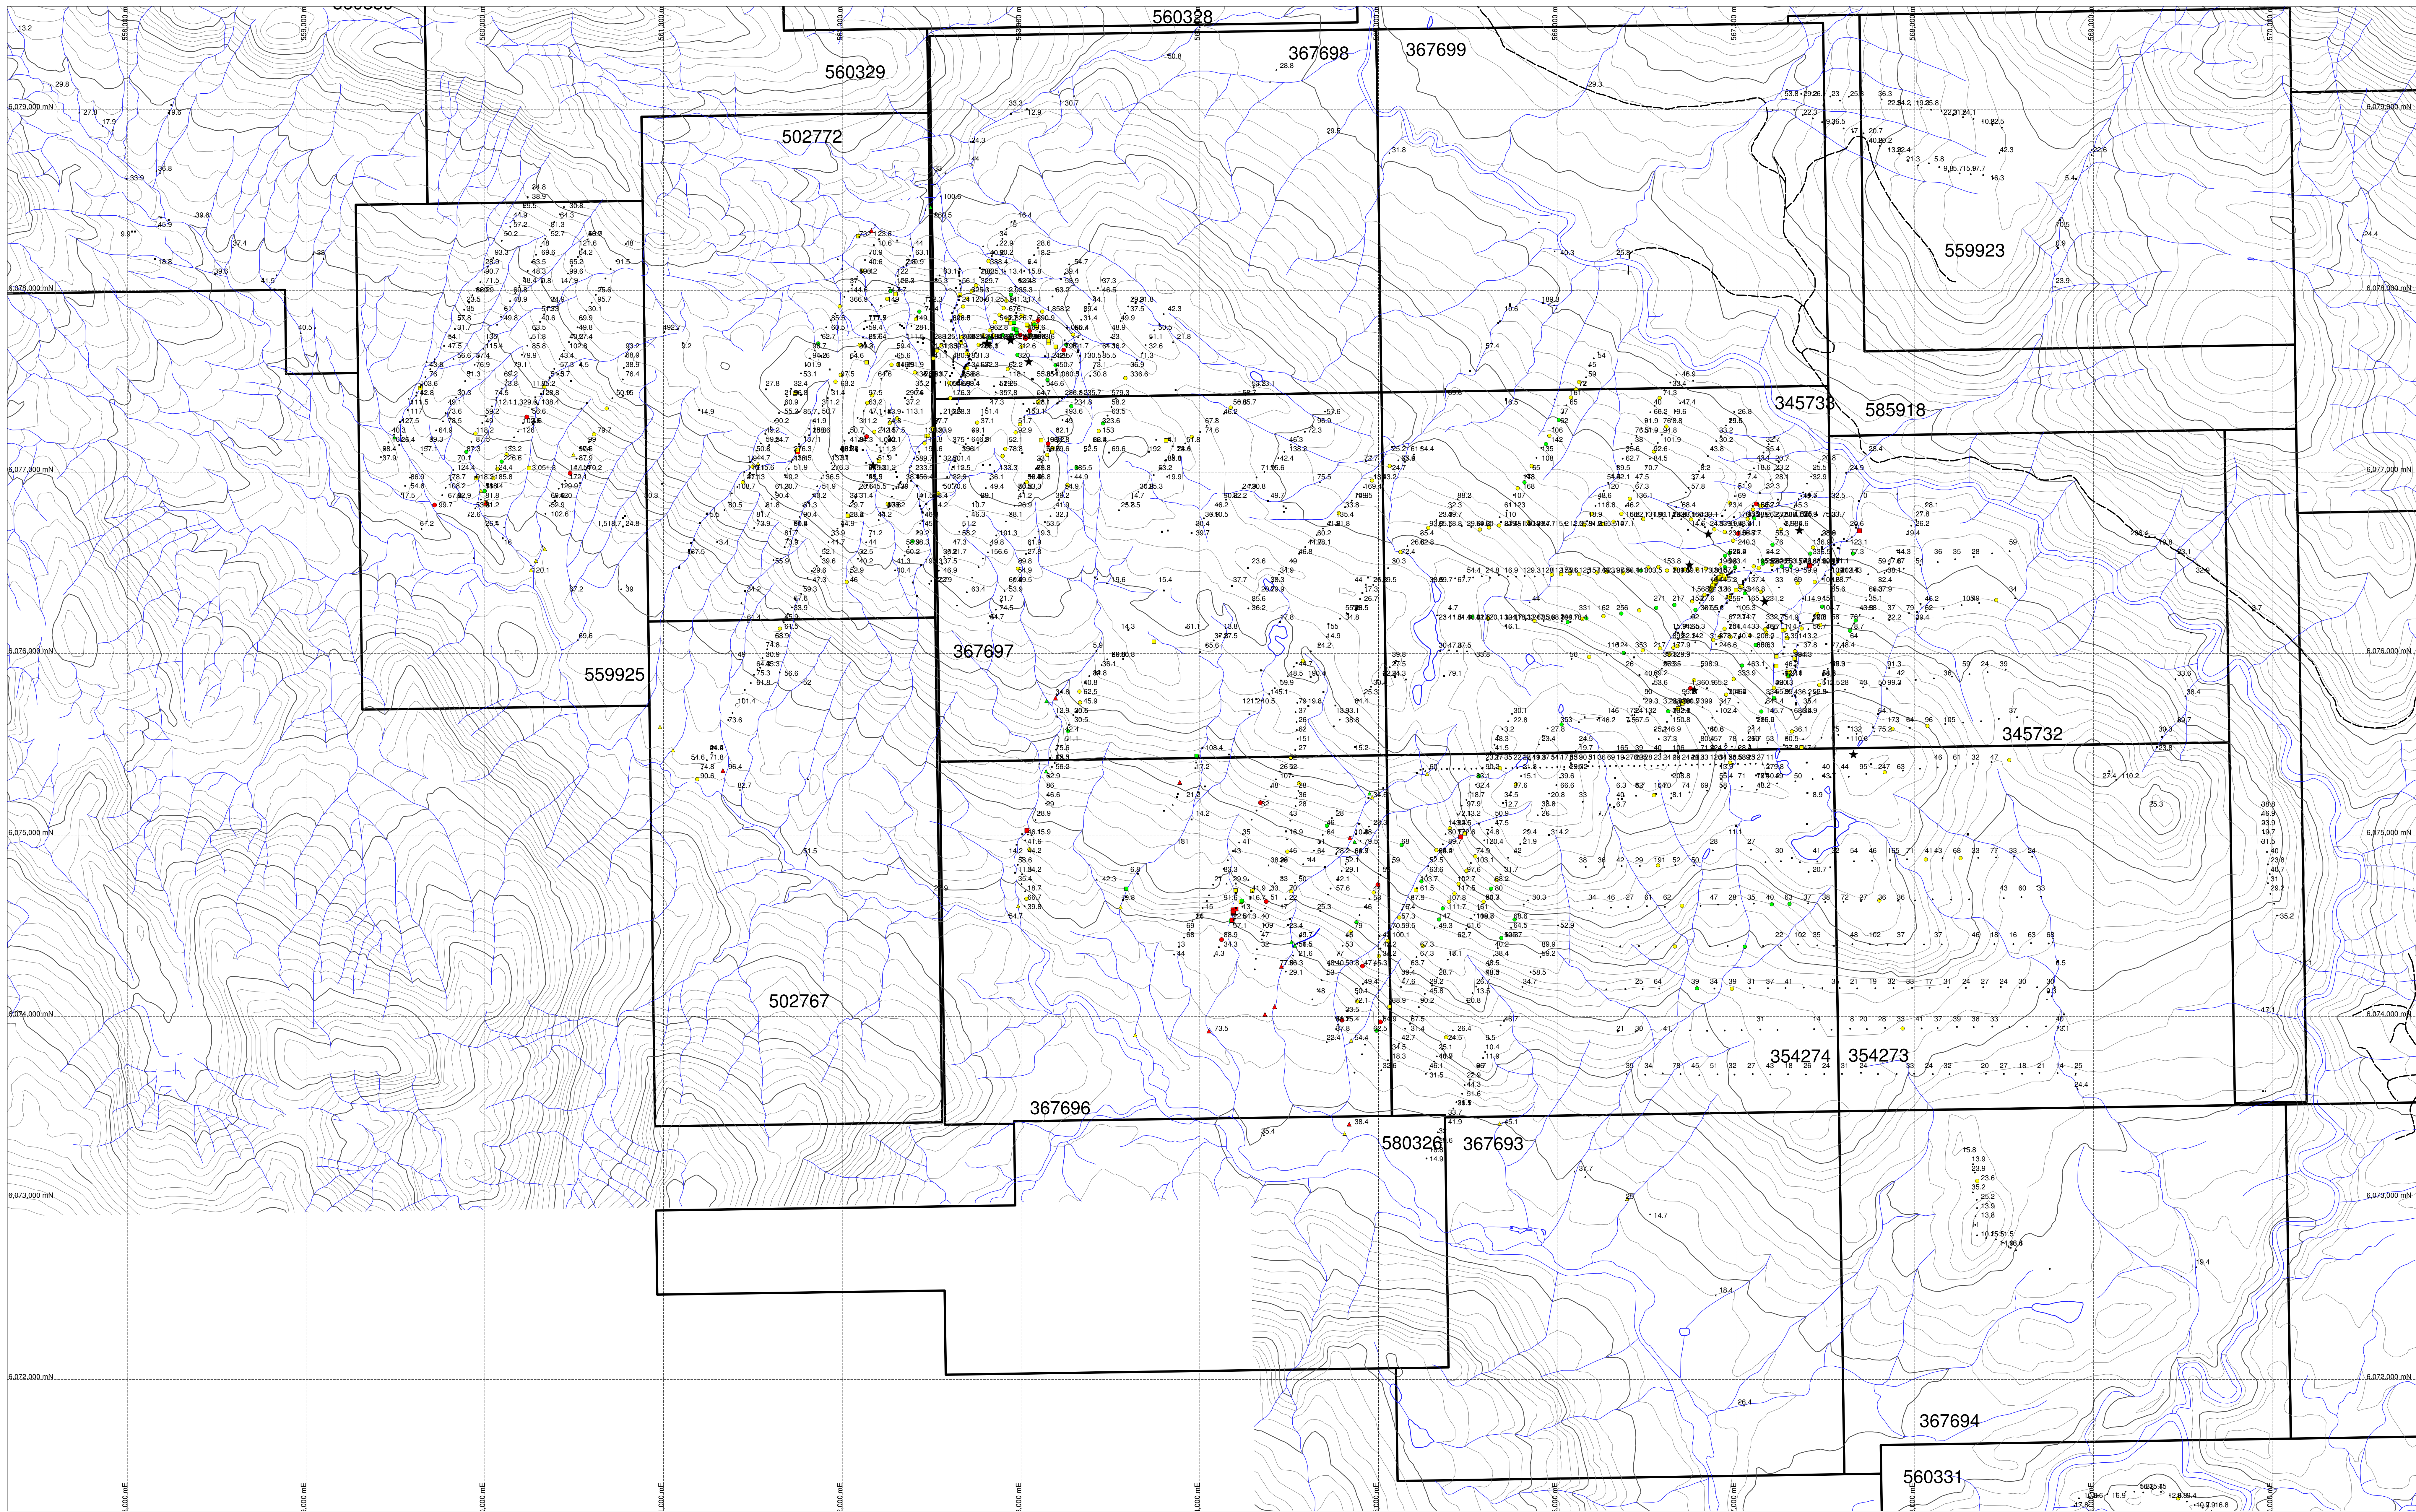


* Diamond Drill Hole

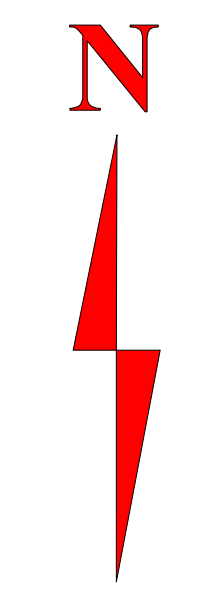

rocks by Au ppb	
■ 1,000 to 17,700 (16)	
■ 500 to 1,000 (10)	
■ 100 to 500 (82)	
■ 0 to 100 (508)	
silt by Au ppb	
▲ 100 to 433 (11)	
▲ 50 to 100 (8)	
▲ 25 to 50 (17)	
▲ 0 to 25 (151)	
recent soils by Au ppb	
● 120 to 592 (20)	
● 30 to 120 (33)	
● 30 to 60 (173)	
● 0 to 30 (1176)	
old soils by Au ppb	
● 60 to 120 (15)	
● 30 to 60 (33)	
● 0 to 30 (285)	


Zymo Project	
Canadian Gold Hunter - Eastfield Resources Au Geochemistry	
Date: 2/2/2009	
Author: RU	
Office:	
Drawn by: 9	
Scale: 1:2500	Projection: UTM Zone 9 (NAD 83)

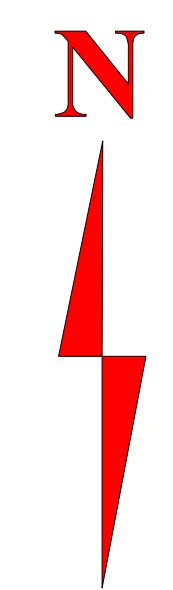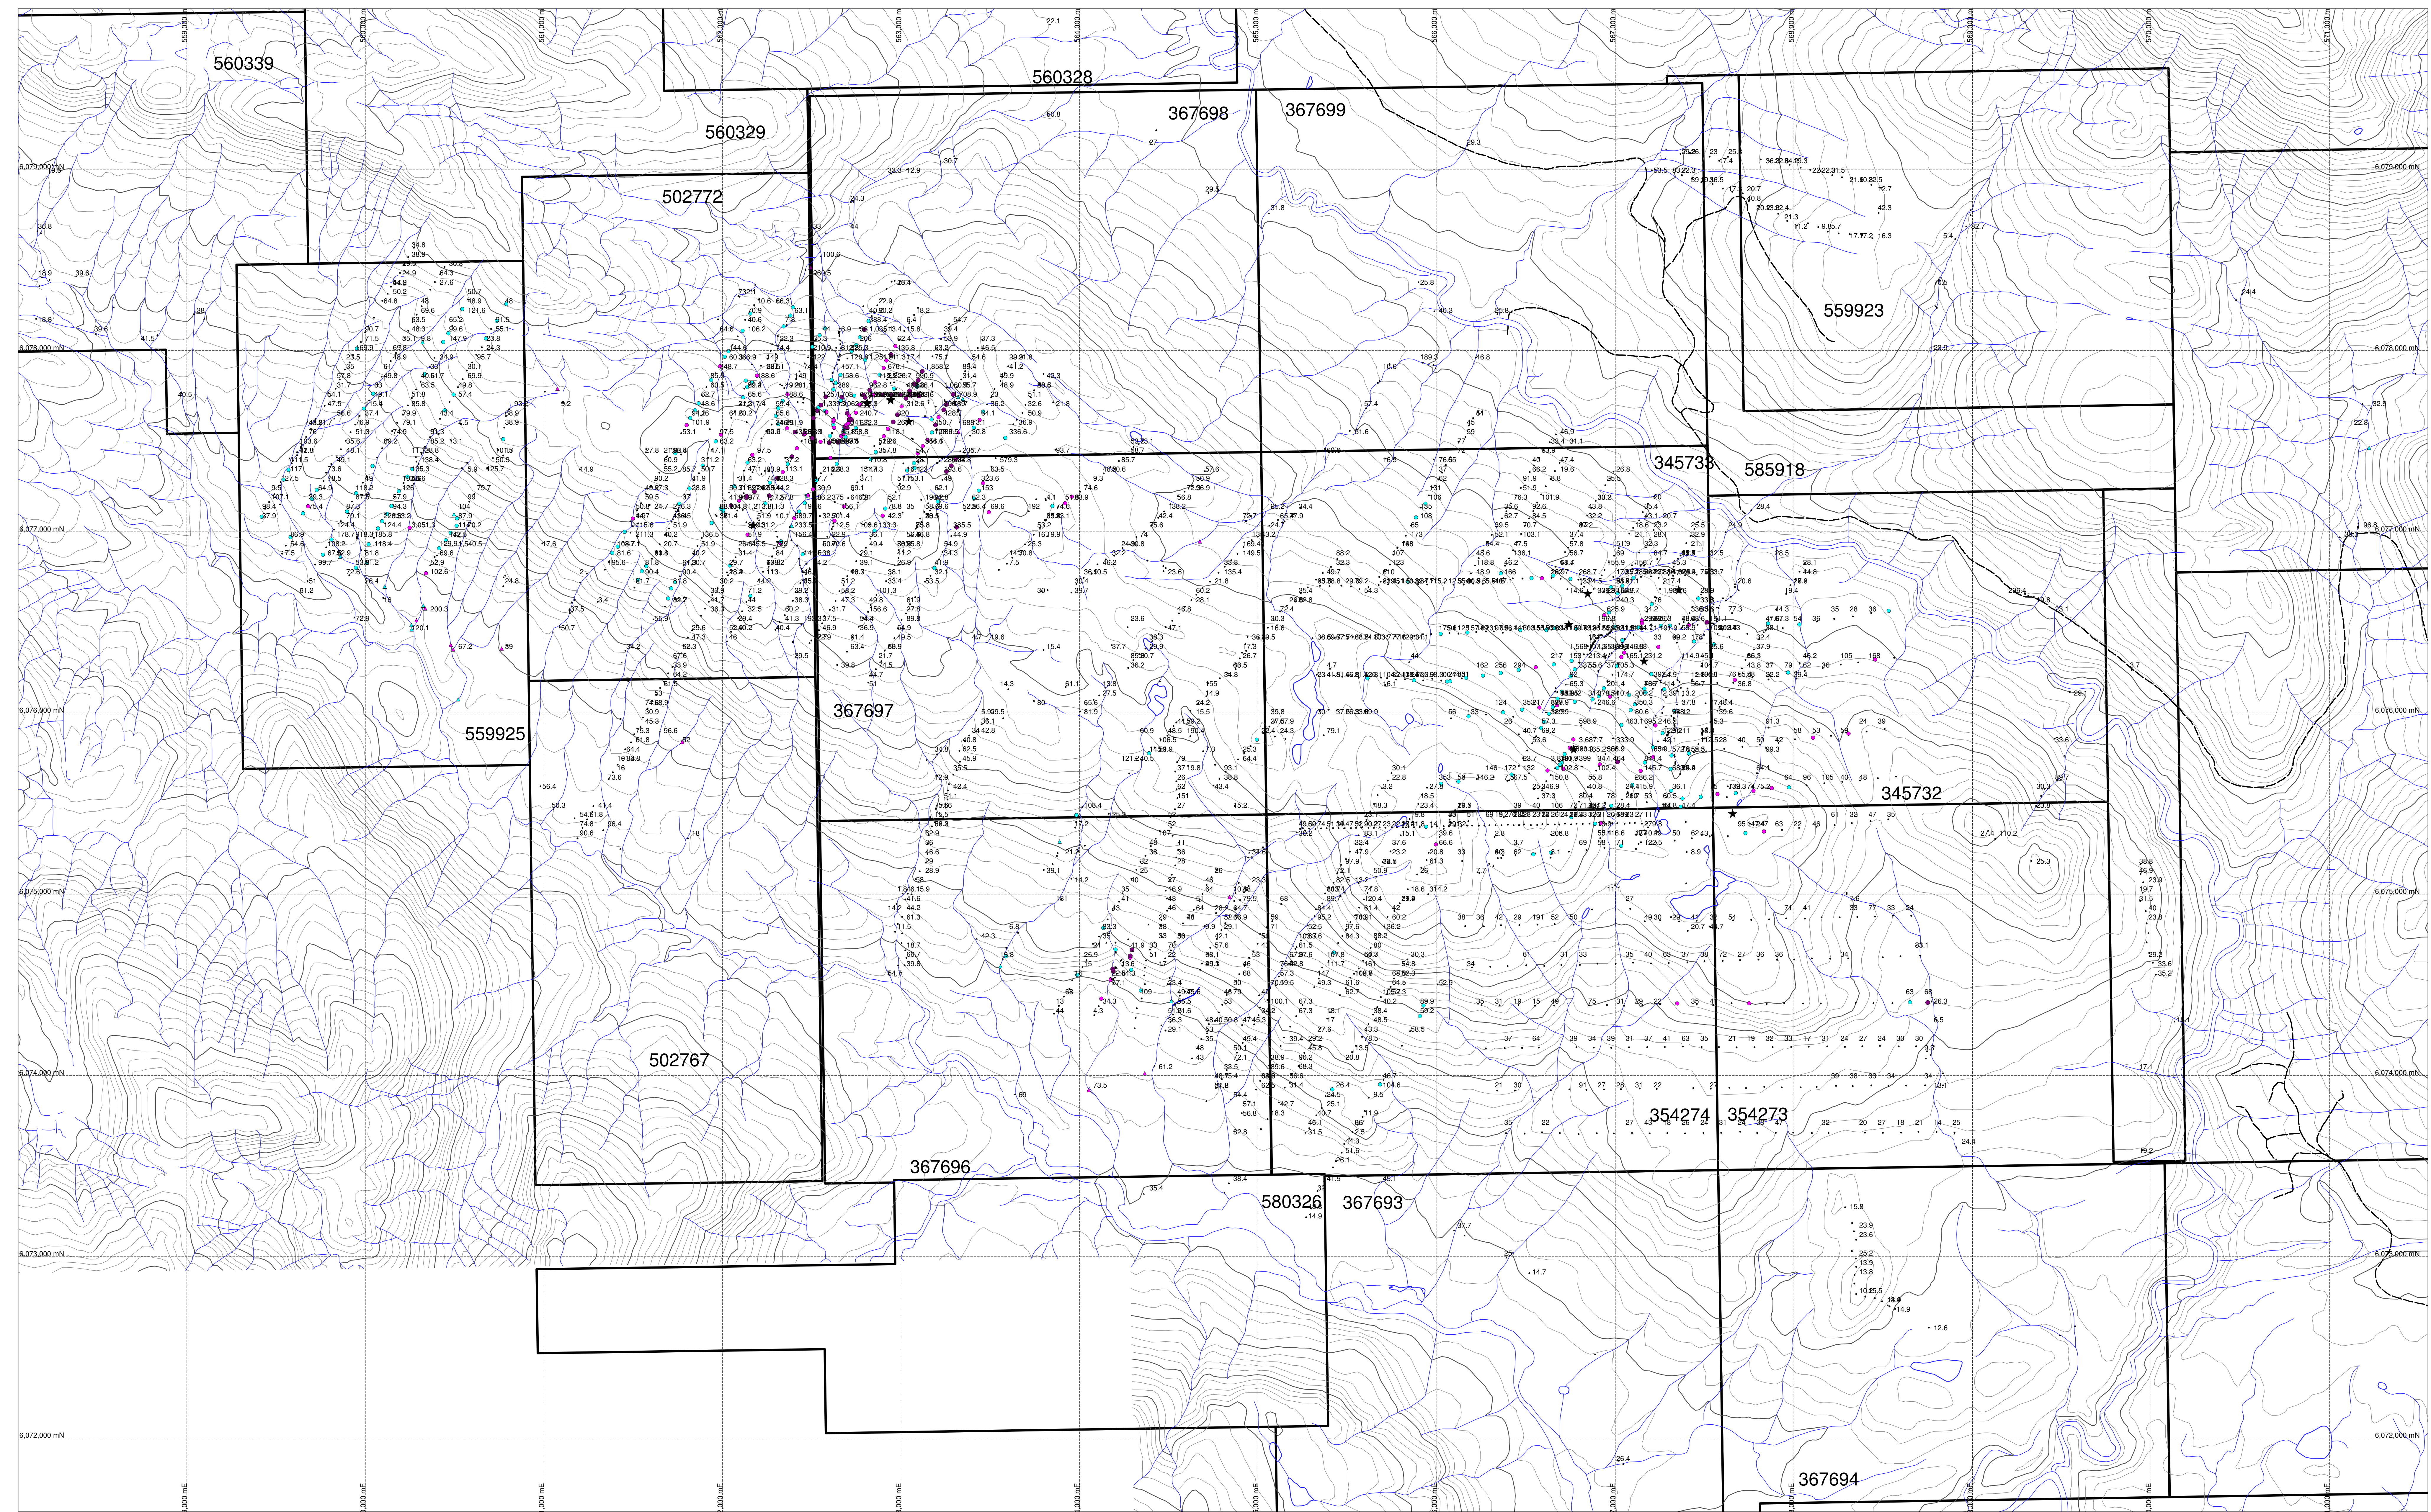

★ Diamond Drill Hole


- rocks by Mo ppm
 - 10 to 39 (9)
 - 50 to 100 (20)
 - 25 to 10 (57)
 - 0 to 25 (550)
- silt by Mo ppm
 - ▲ 10 to 16 (7)
 - ▲ 8 to 10 (12)
 - ▲ 4 to 8 (14)
 - ▲ 0 to 4 (157)
- recent soils by Mo ppm
 - 20 to 153 (42)
 - 10 to 25 (54)
 - 5 to 10 (172)
 - 0 to 5 (1154)
- old soils by Mo ppm
 - 20 to 306 (2)
 - 10 to 25 (21)
 - 5 to 10 (96)
 - 0 to 5 (274)

Date: 2/2/2009	Zymo Project Canadian Gold Hunter - Eastfield Resources Mo Geochemistry
Author: RJ	
Office:	
Drawing: 10	
Scale: 1:12500	Projection: UTM Zone 9 (NAD 83)

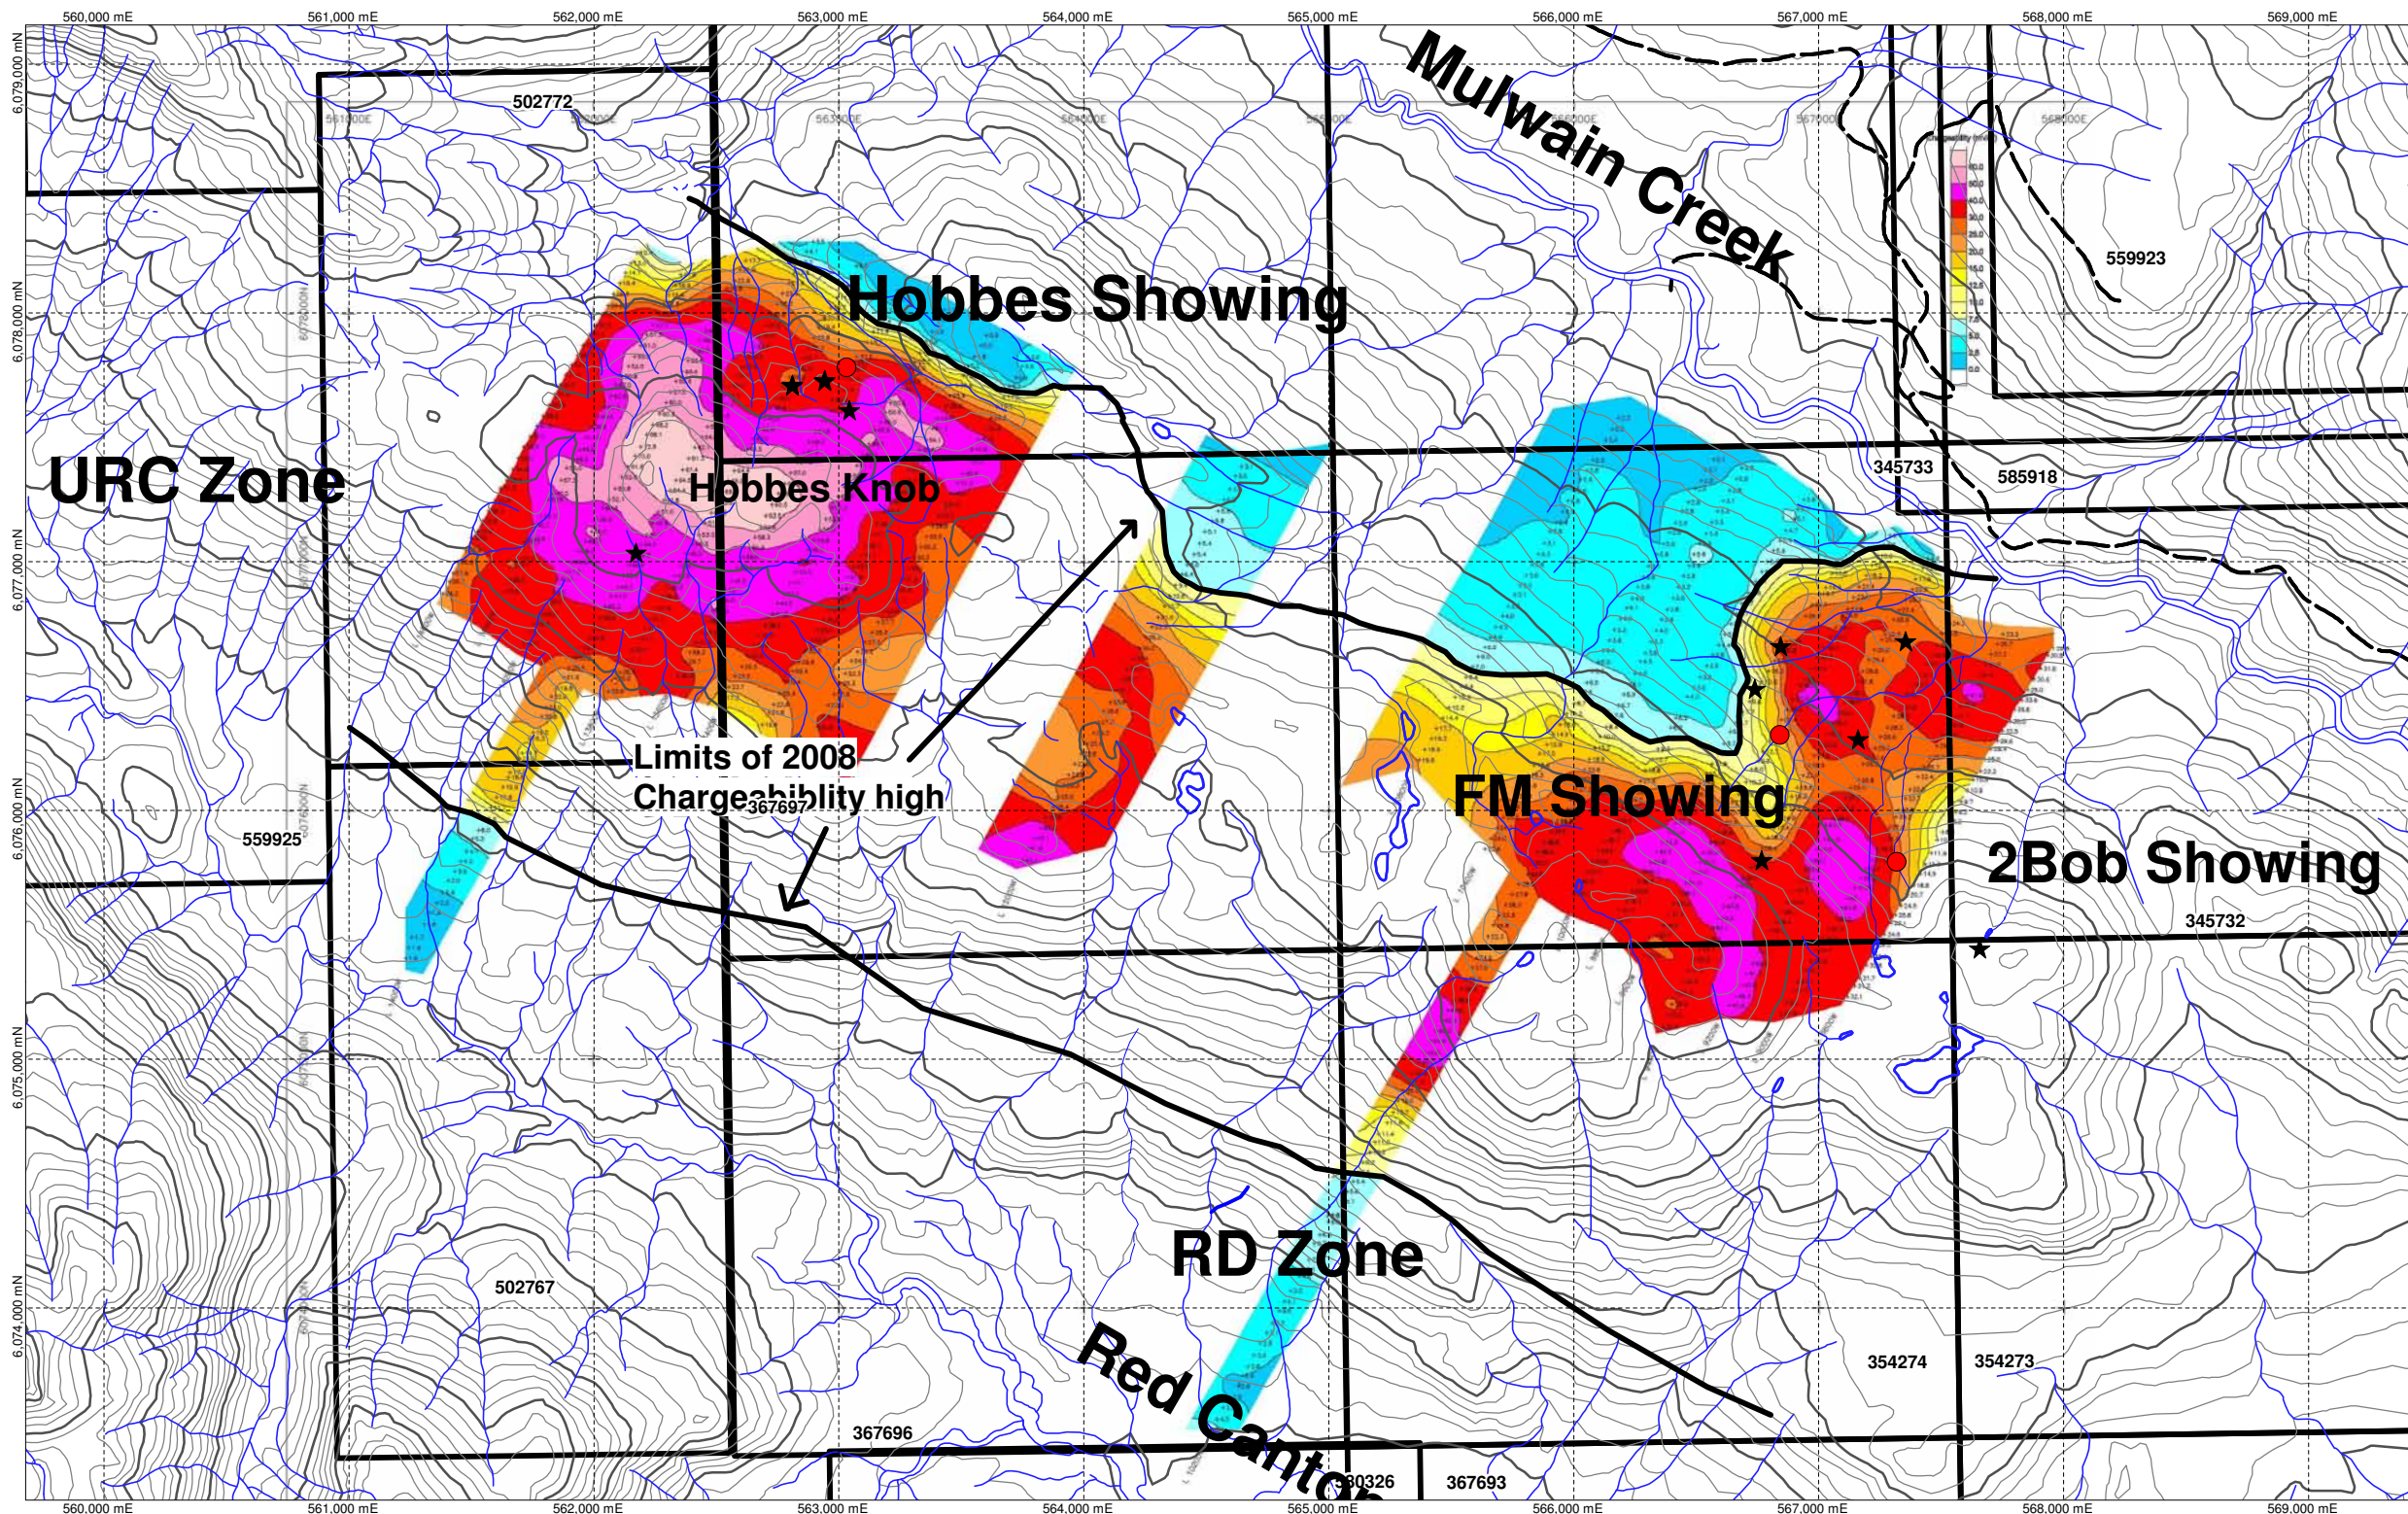

- LEGEND**
- ★ Diamond Drill Hole
 - Named Showing


Zymo Project Canadian Gold Hunter - Eastfield Resources Chargeability 2008	
Date: 31/1/2009	
Author: bobj	
Office:	
Drawing: 11	
Scale: 1:30000	Projection: UTM Zone 9 (NAD 83)

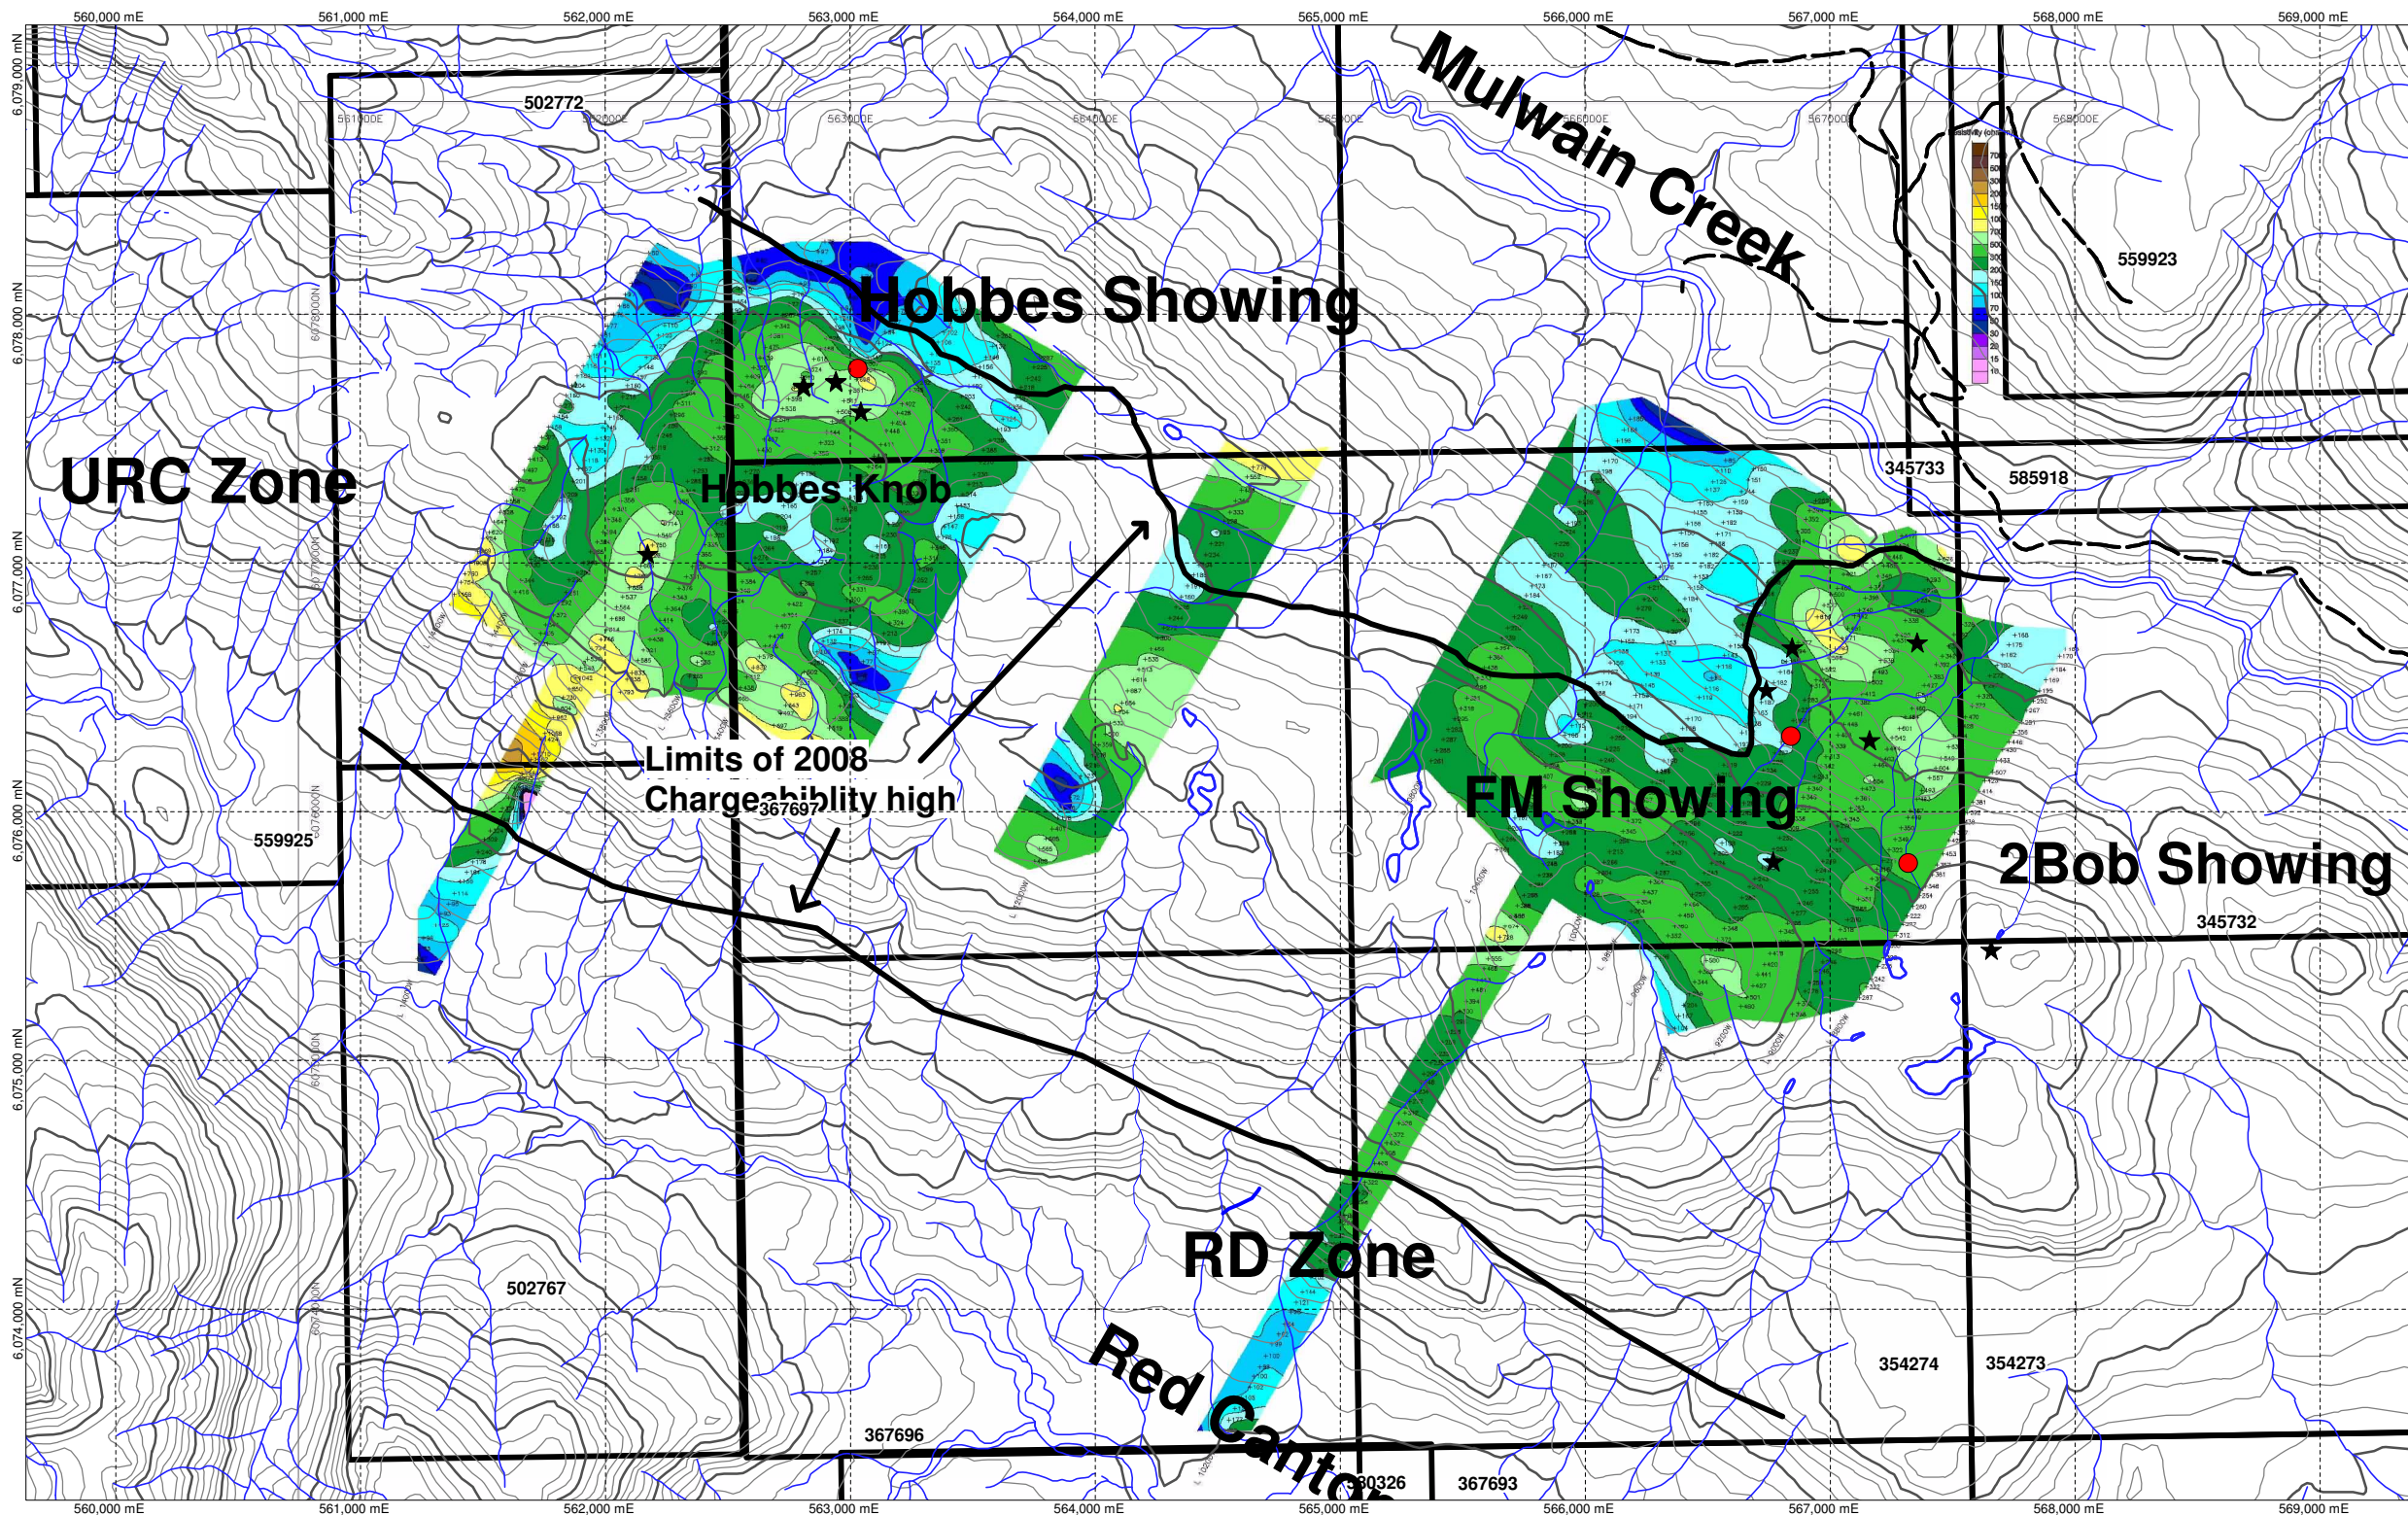

LEGEND

- ★ Diamond Drill Hole
- Named Showing



Zymo Project Canadain Gold Hunter - Eastfield Resources Resistivity 2008	
Date: 31/1/2009 Author: bobj Office: Drawing: 12 Scale: 1:20000 Projection: UTM Zone 9 (NAD 83)	

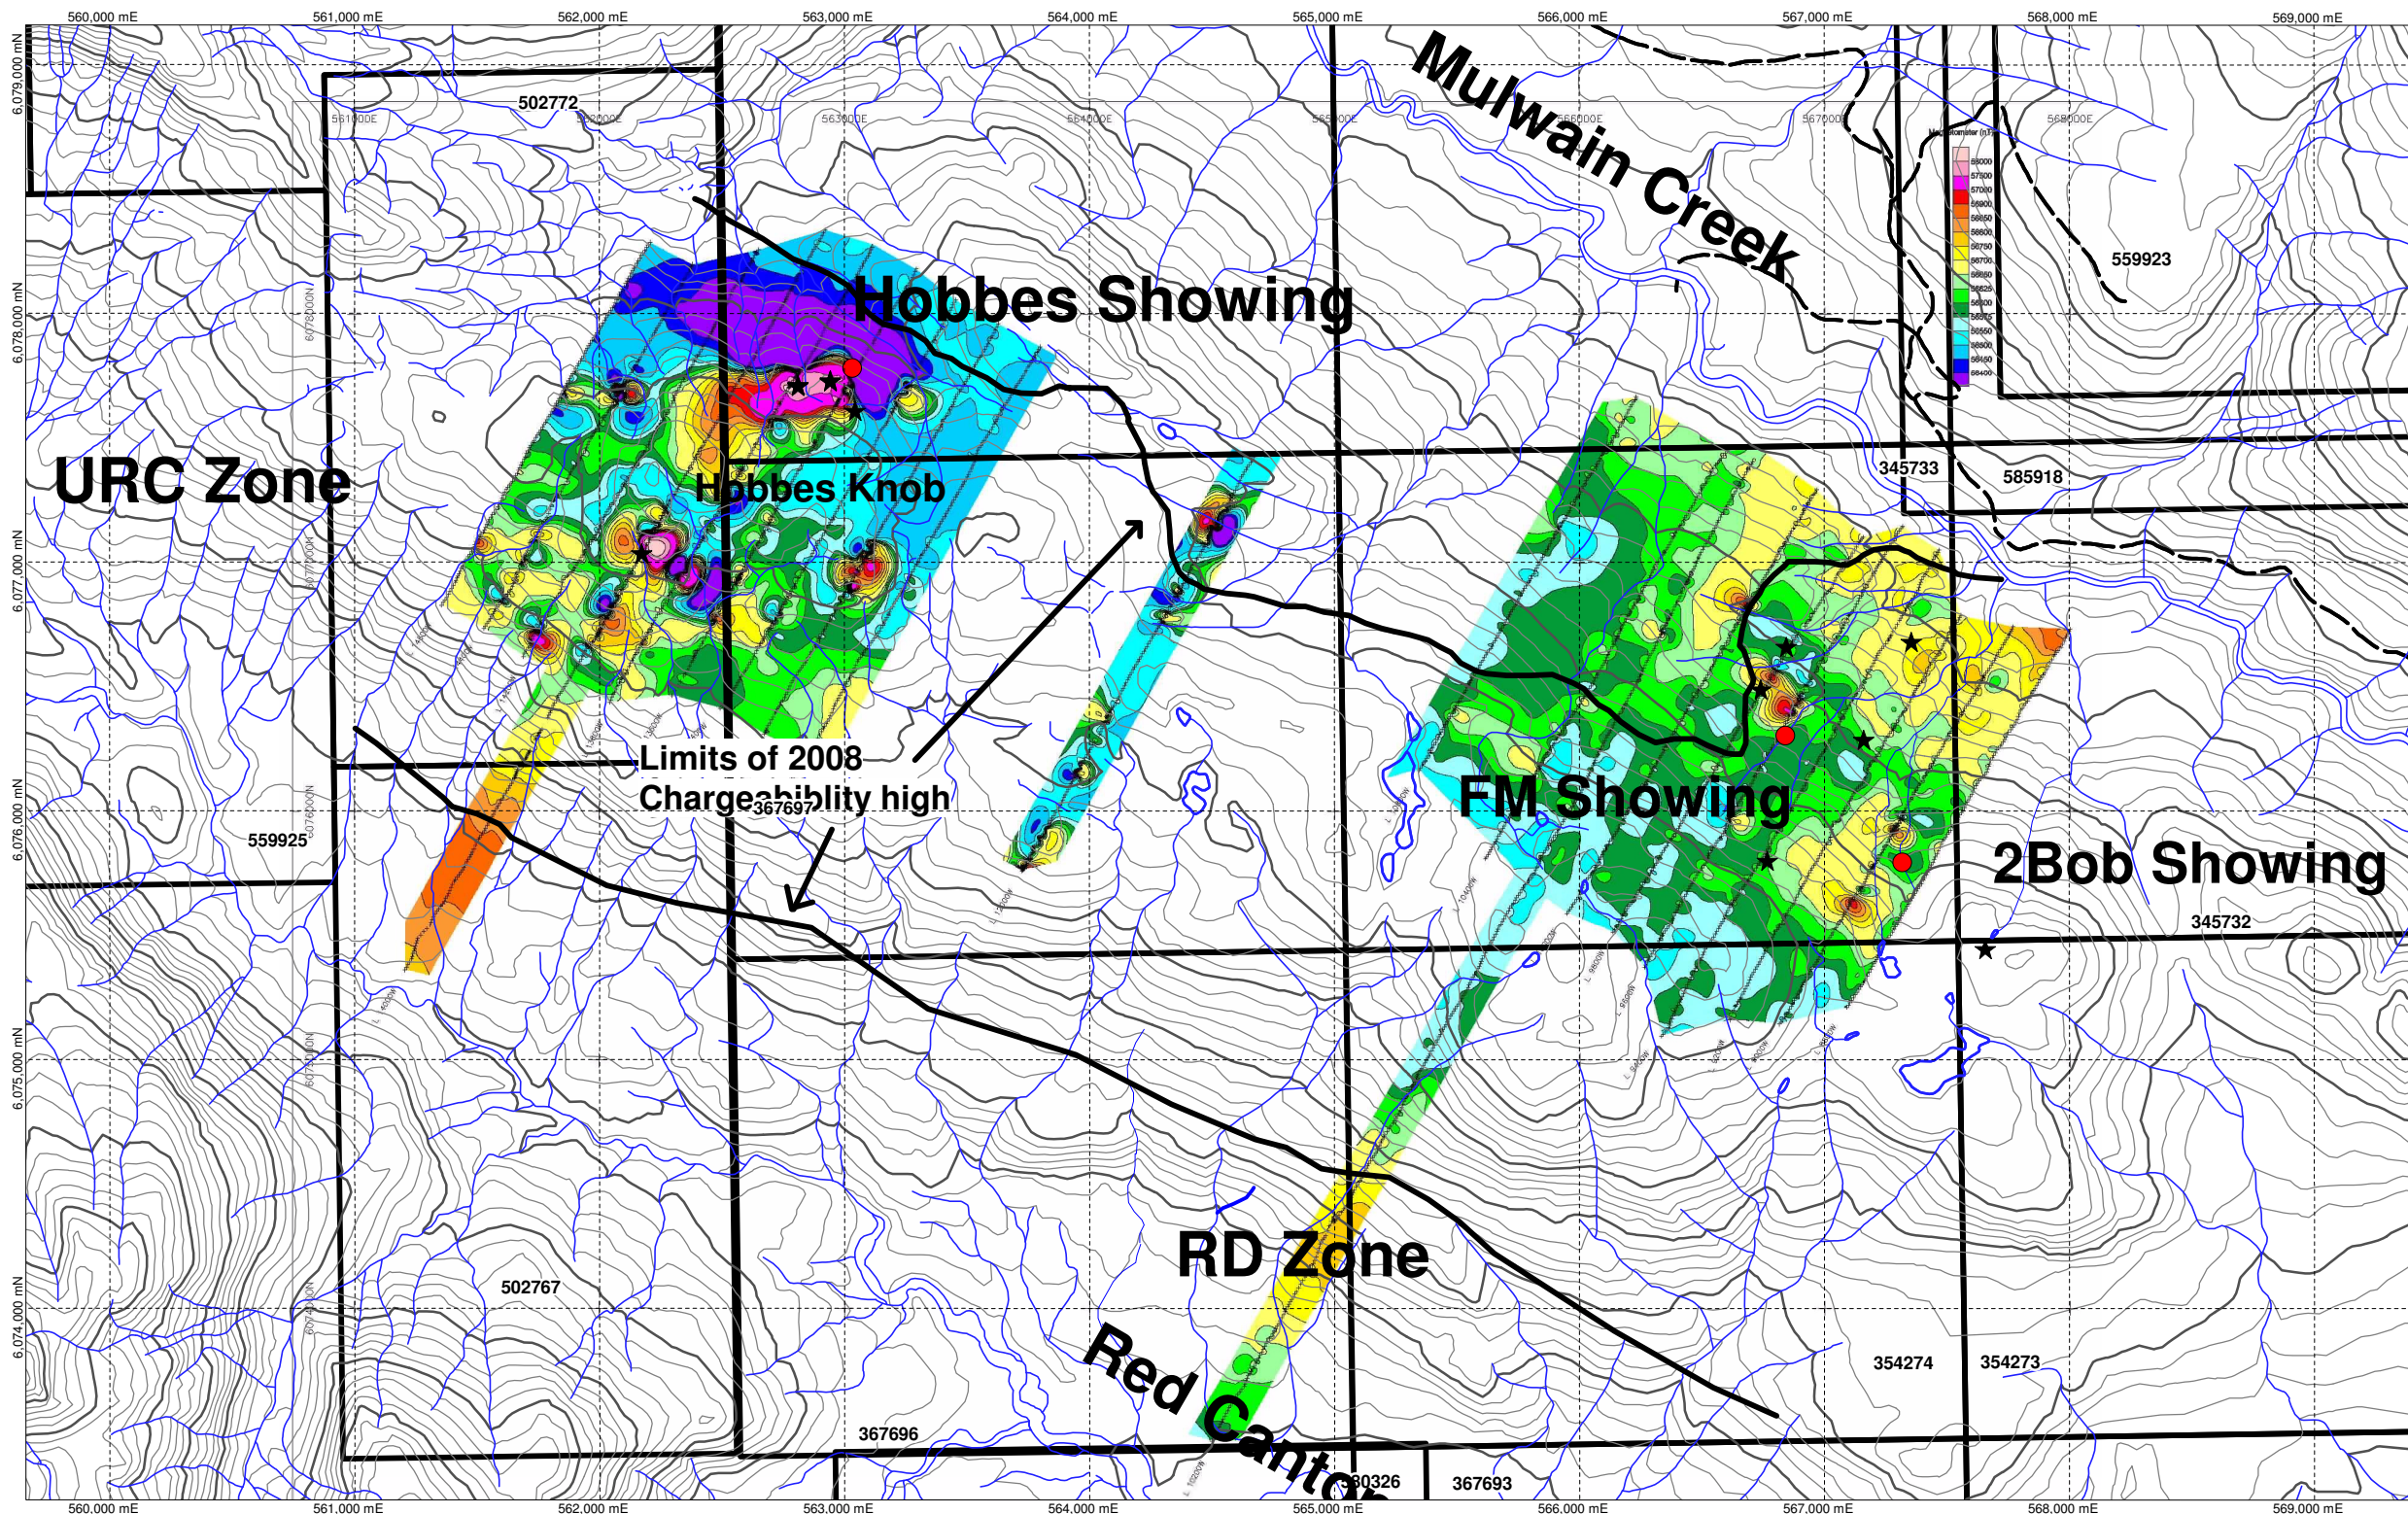

LEGEND


- ★ Diamond Drill Hole
- Named Showing

<p>Zymo Project Canadian Gold Hunter - Eastfield Resources Ground Magnetics 2008</p>	
<p>Date: 3/1/2009 Author: bobj Office: Drawing: 13 Scale: 1:30000 Projection: UTM Zone 9 (NAD 83)</p>	<p>0 250 500 1,000 metres</p>

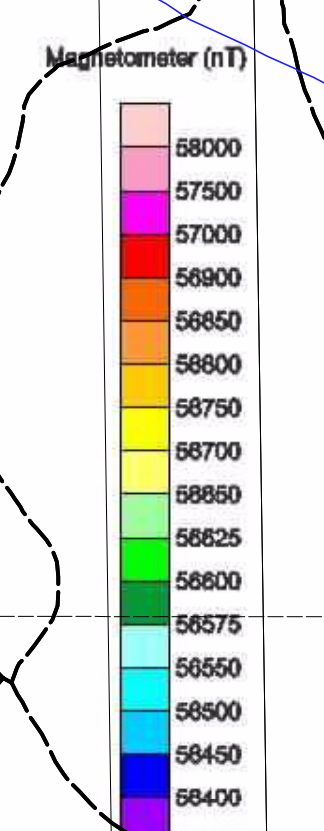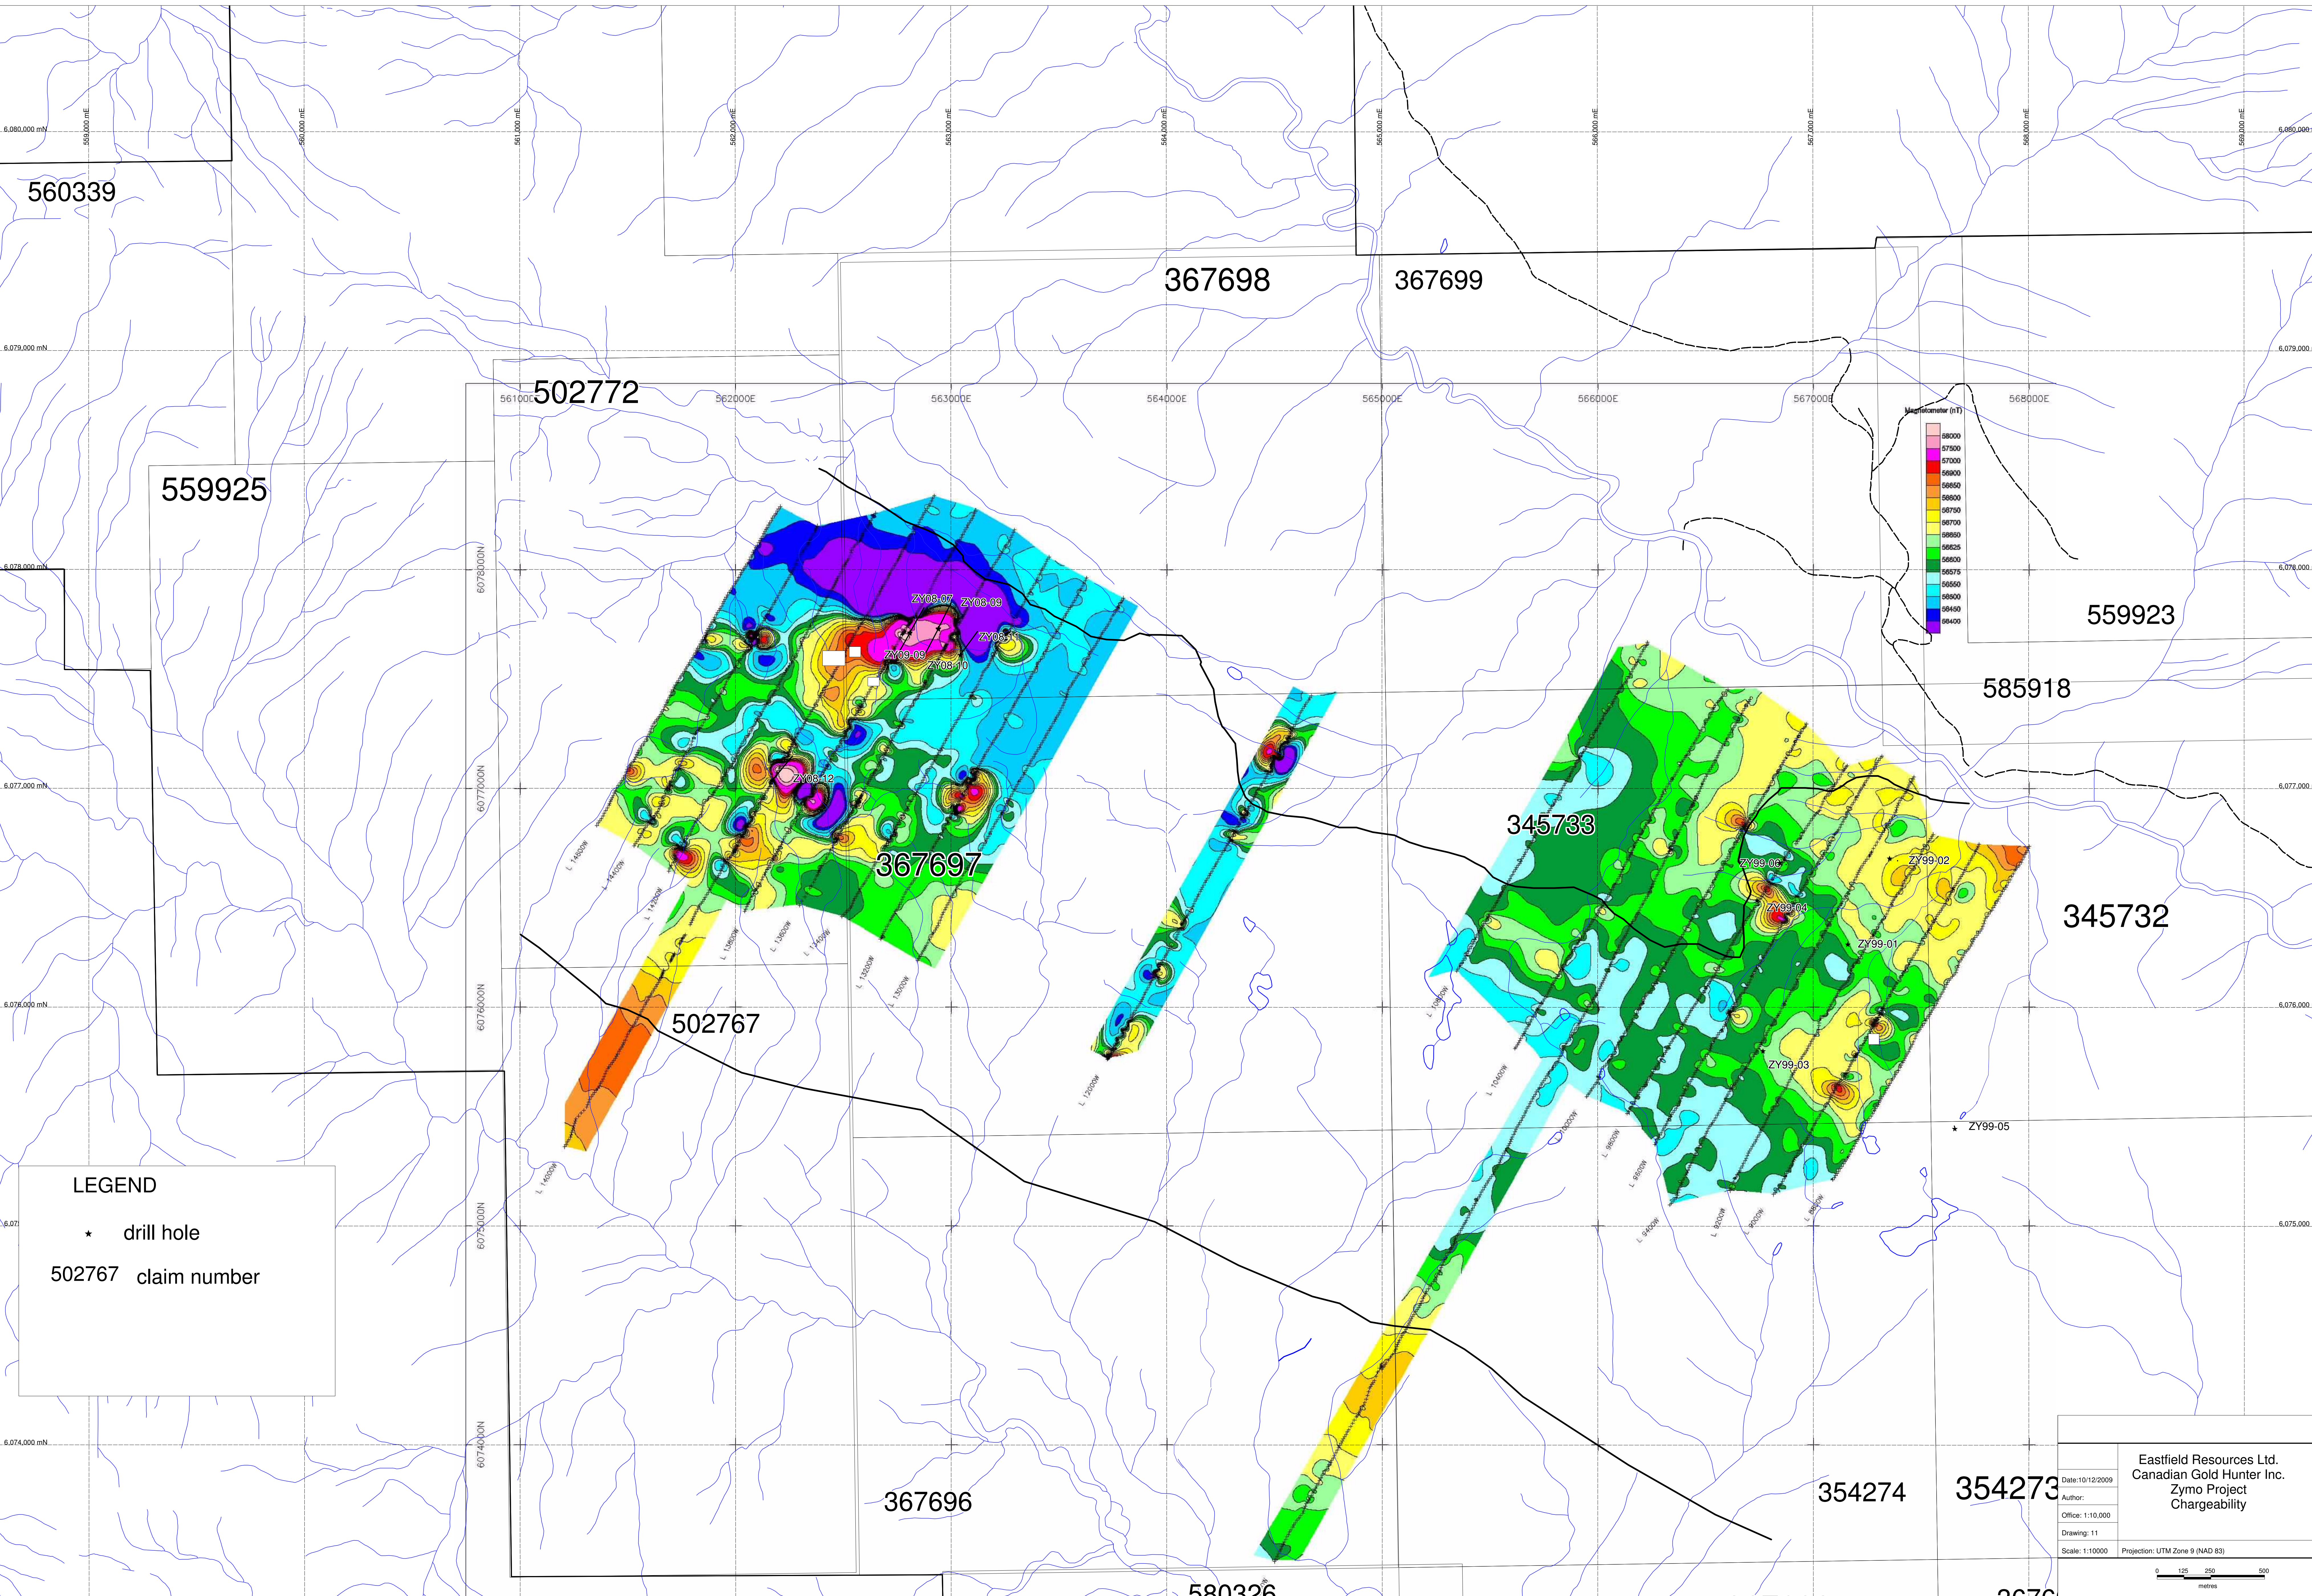

LEGEND
 * drill hole
 502767 claim number

Eastfield Resources Ltd. Canadian Gold Hunter Inc. Zymo Project Chargeability	
Date: 10/12/2009	
Author:	
Office: 1:10,000	
Drawing: 11	
Scale: 1:10000	Projection: UTM Zone 9 (NAD 83)

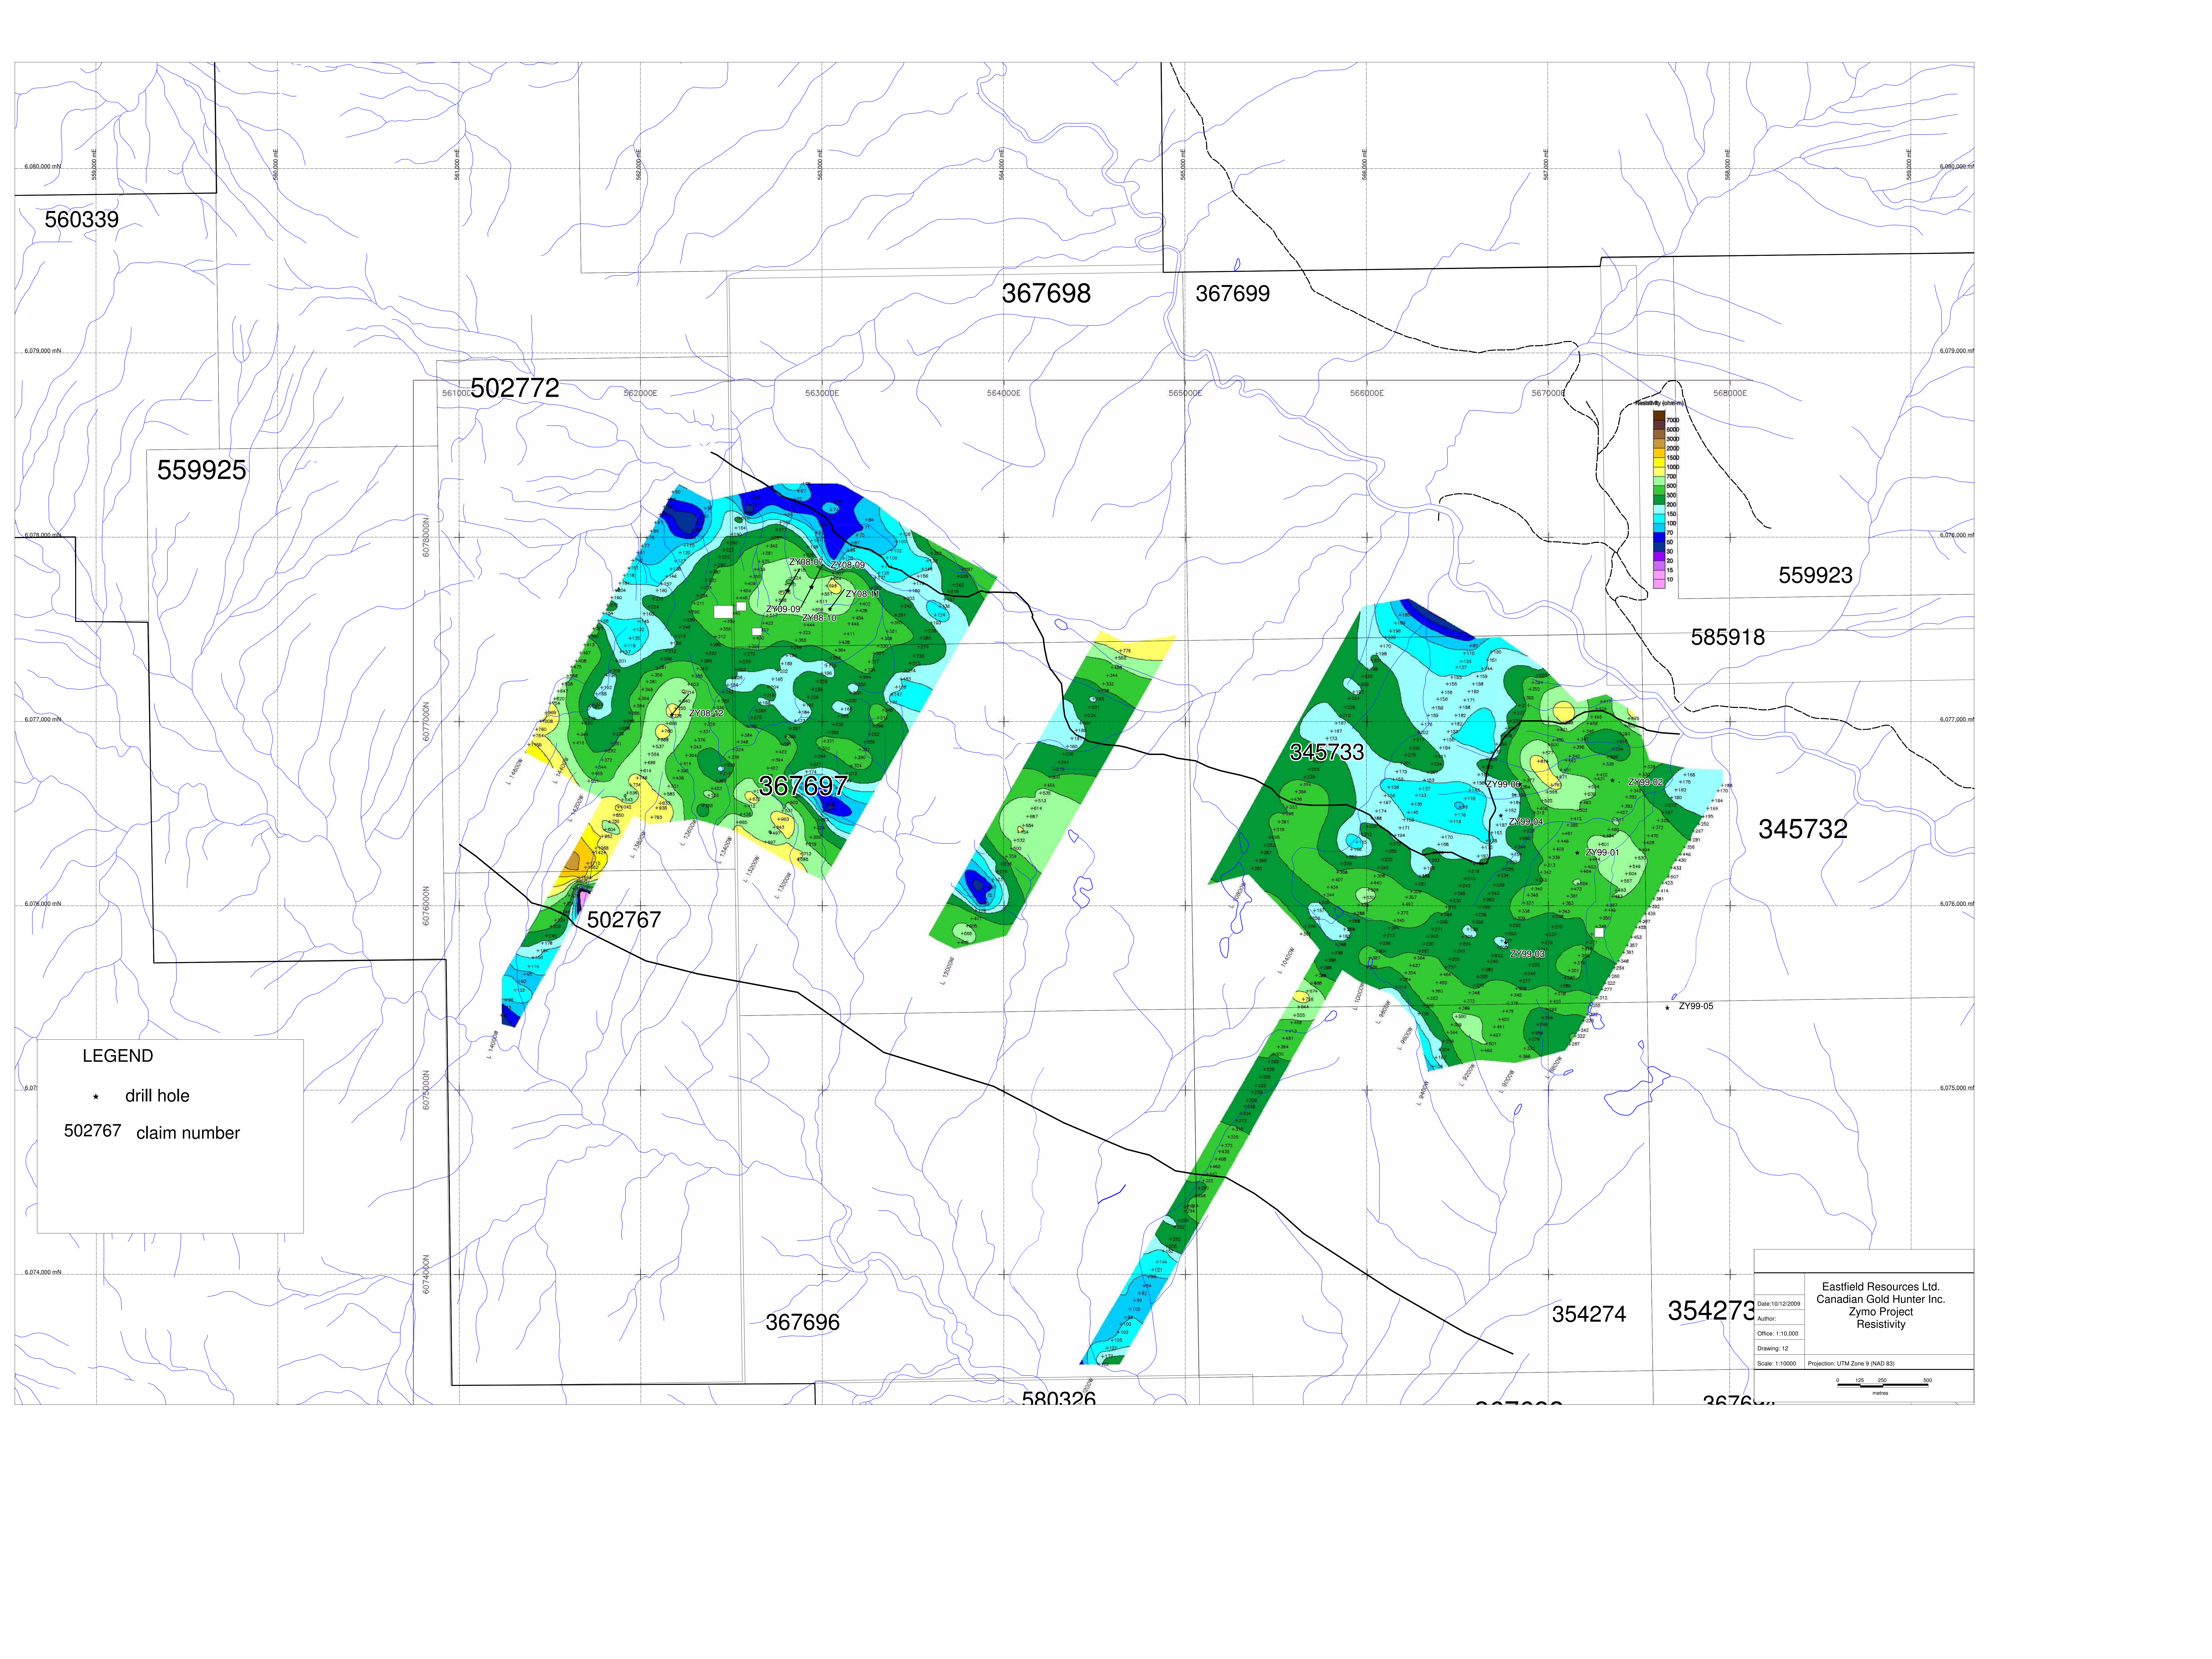

560339

367698

367699

502772

559925

559923

585918

502767

367697

345733

345732

367696


580326

354274



354273

267694

LEGEND
 * drill hole
 502767 claim number

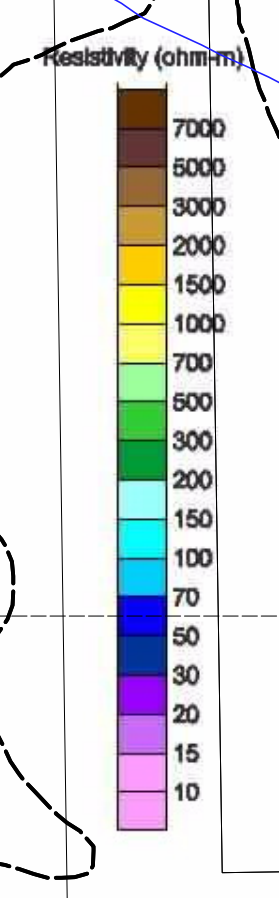



Eastfield Resources Ltd.
 Canadian Gold Hunter Inc.
 Zymo Project Resistivity
 Date: 10/12/2009
 Author:
 Office: 1:10,000
 Drawing: 12
 Scale: 1:10000 Projection: UTM Zone 9 (NAD 83)

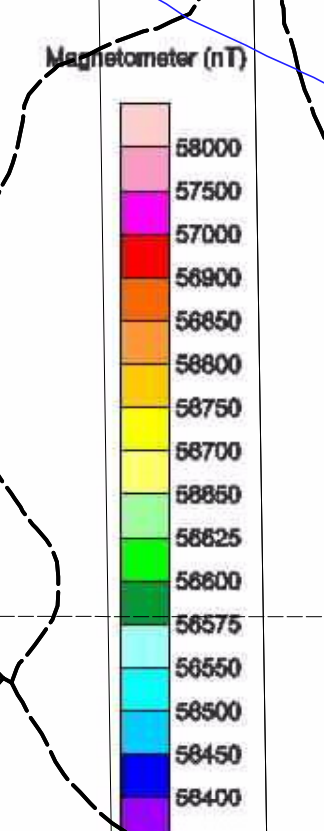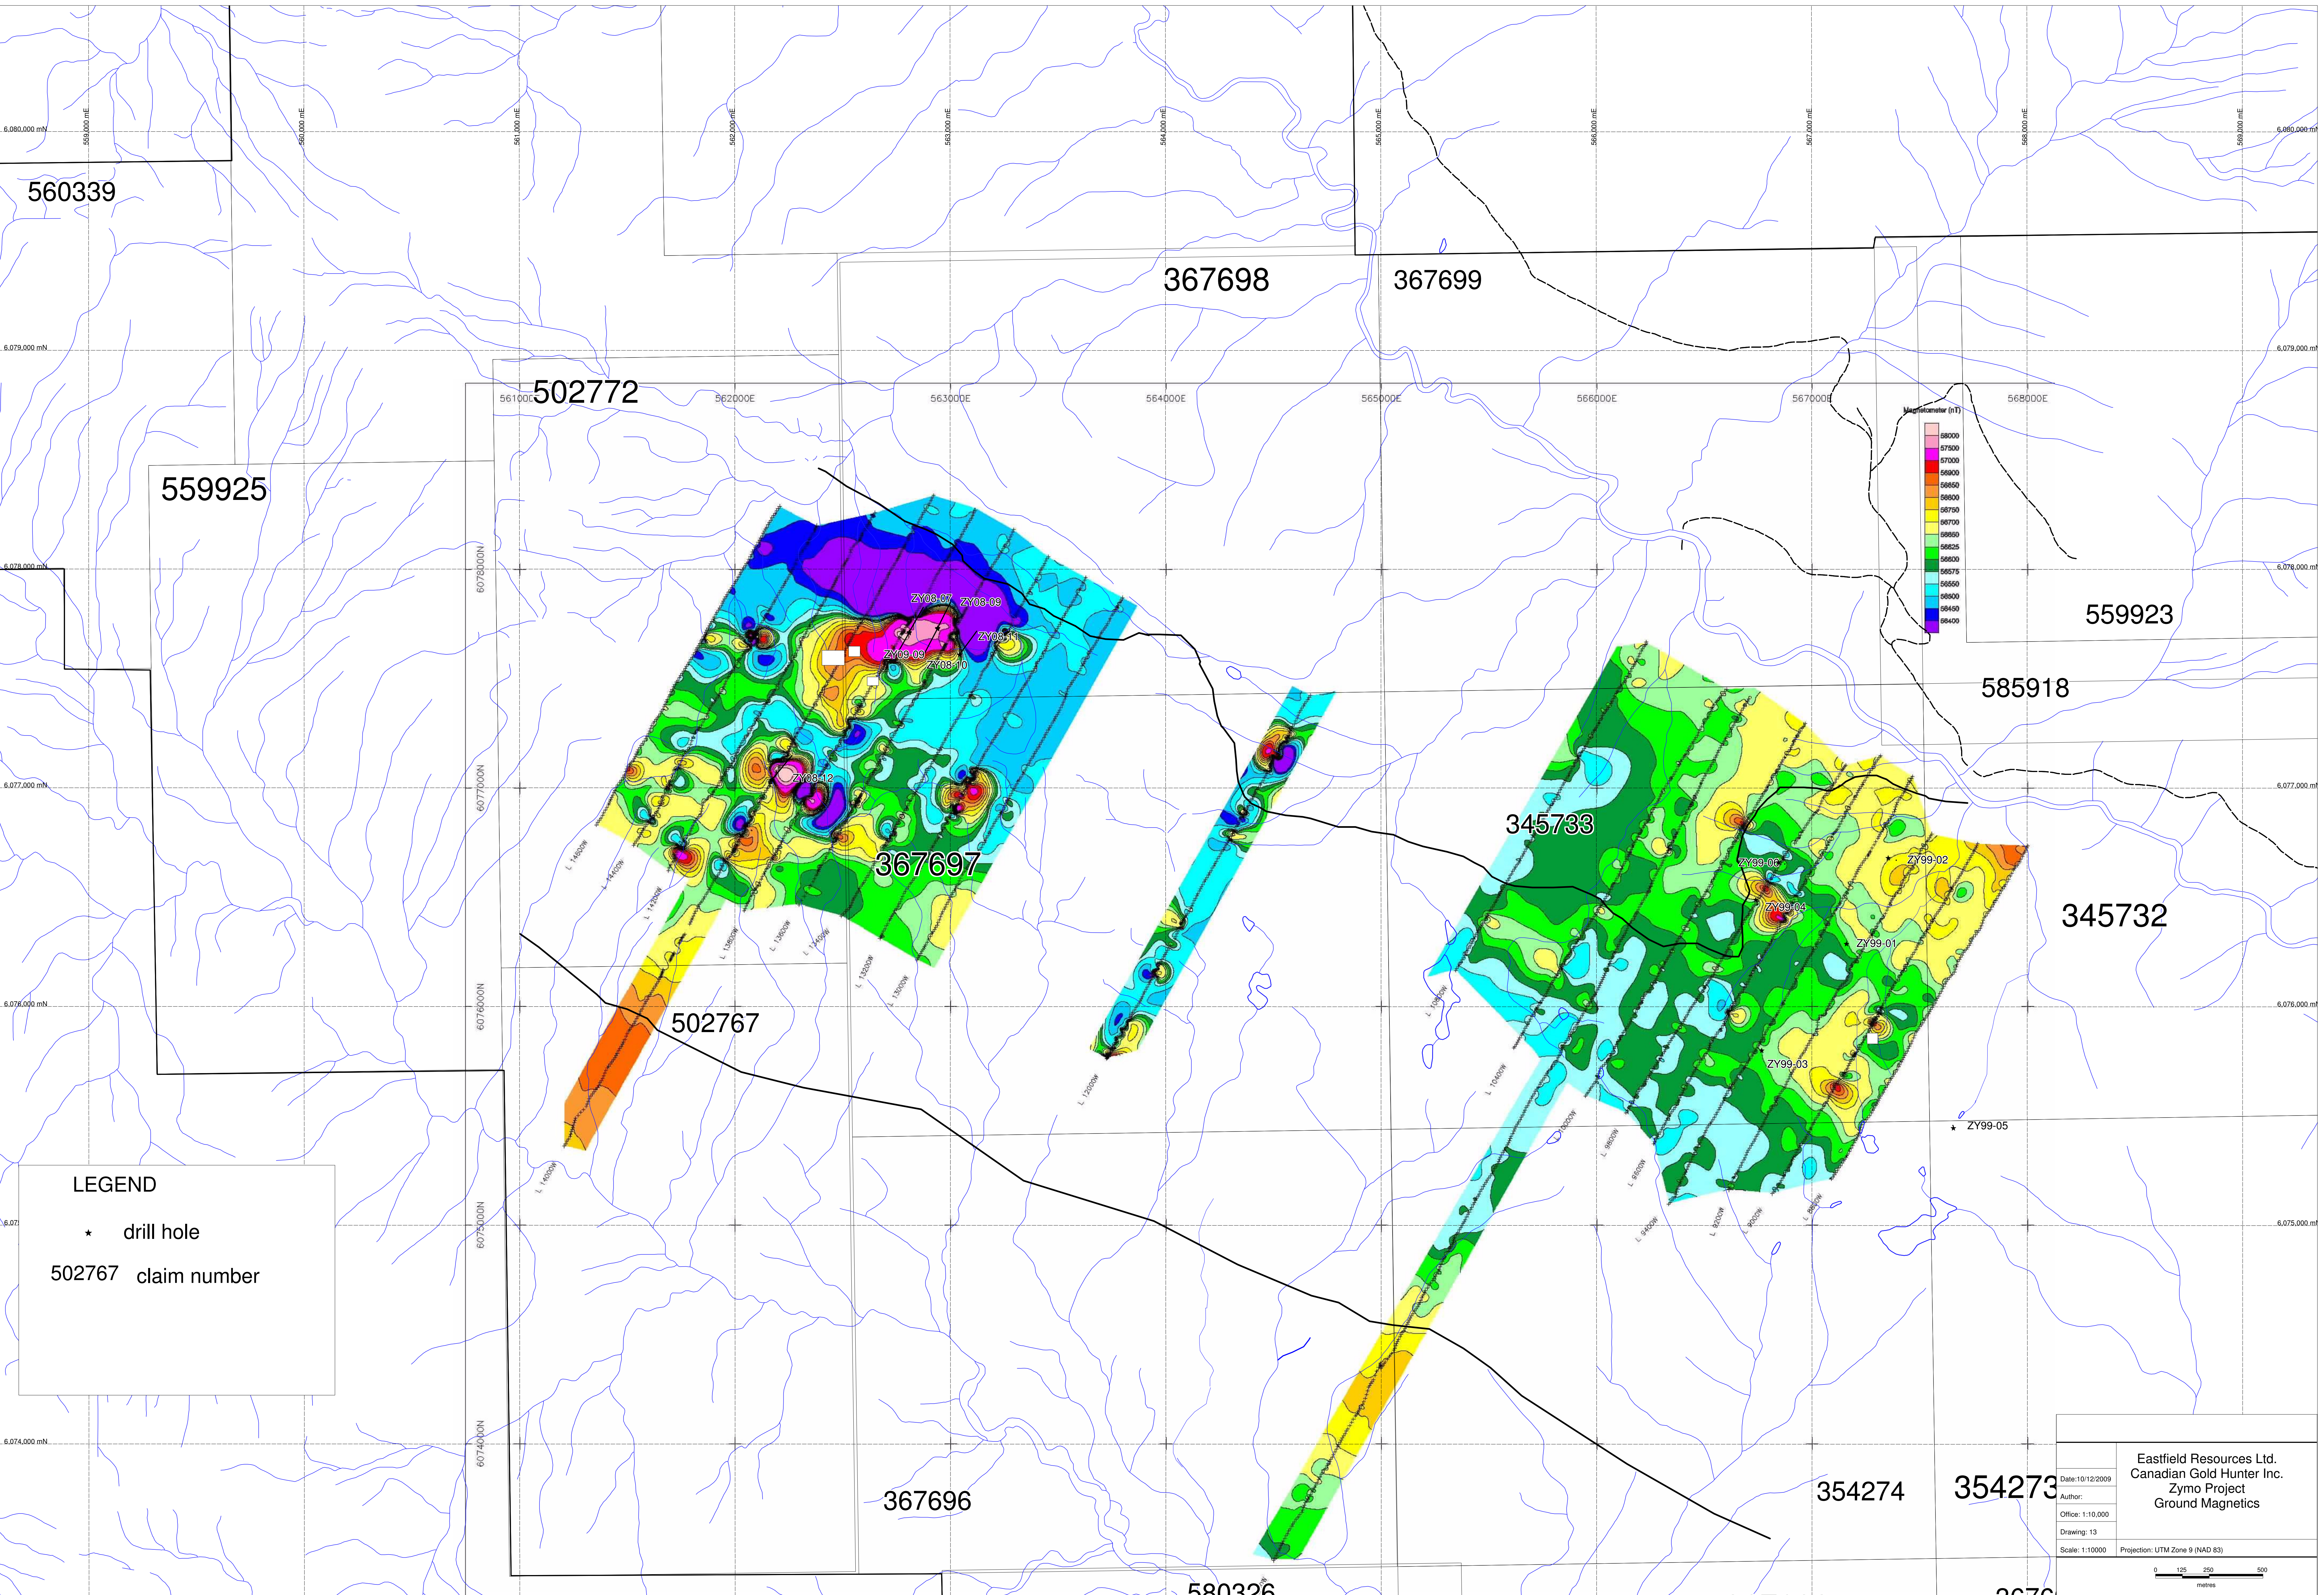

LEGEND
 * drill hole
 502767 claim number

Eastfield Resources Ltd. Canadian Gold Hunter Inc. Zymo Project Ground Magnetics	
Date: 10/12/2009	Author:
Office: 1:10,000	Drawing: 13
Scale: 1:10000	Projection: UTM Zone 9 (NAD 83)

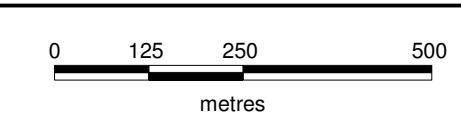

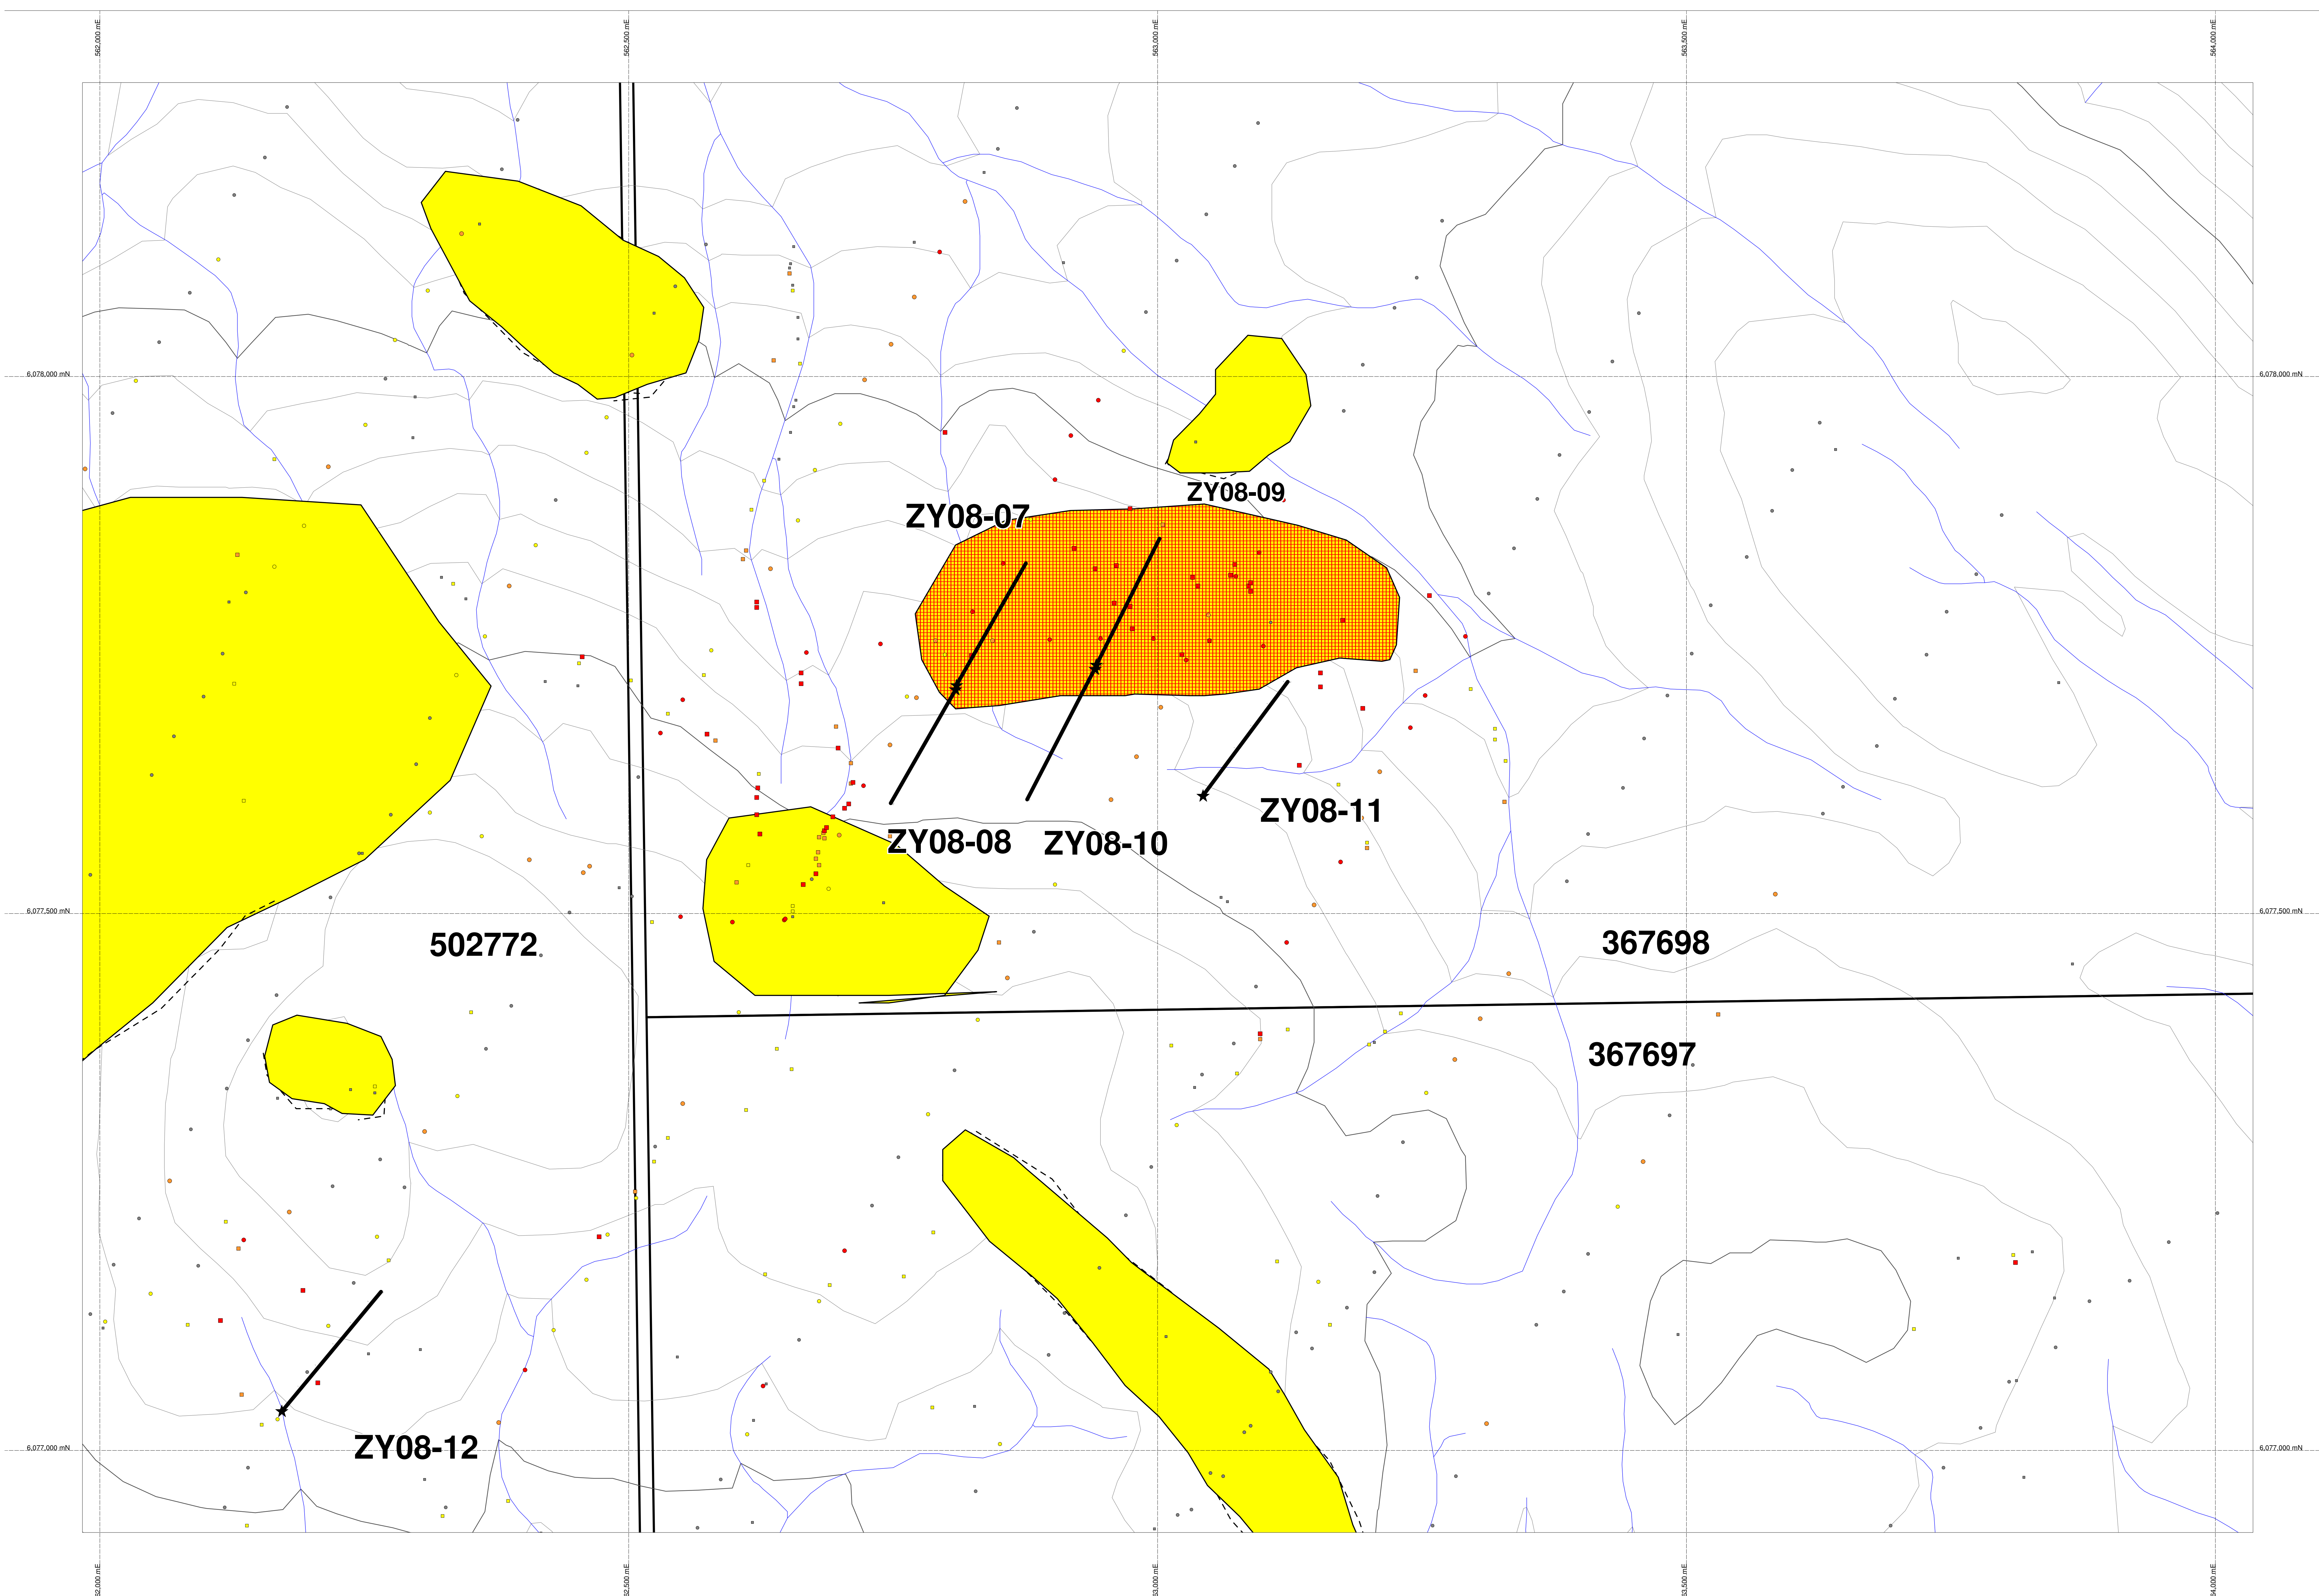

zymo_eff_rocks by Cu

- 1,000 to 10,000 (38)
- 500 to 1,000 (60)
- 100 to 500 (141)
- 0 to 100 (328)

zymo_eff_soils by Cu


- 500 to 4,000 (46)
- 200 to 500 (83)
- 100 to 200 (200)
- 0 to 100 (1098)

* ZY08-07 2008 Drill hole


367698 Claim number


qtz-mgt alt diorite porphyry

chl alt diorite porphyry



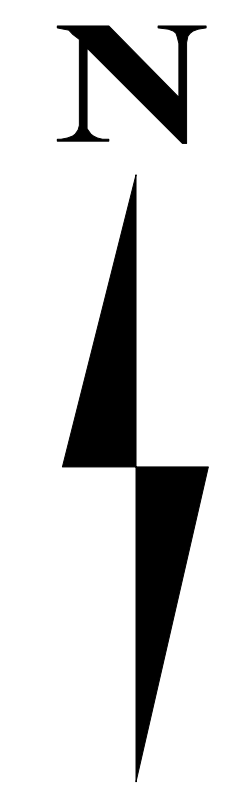



Zymo Property Canadian Gold Hunter - Eastfield Resources Hobbes Zone Drill Hole Locations	
Date: 4/2/2009	Author: JAJ
Office:	Drawing: 14
Scale: 1:2500	Projection: UTM Zone 9 (NAD 83)

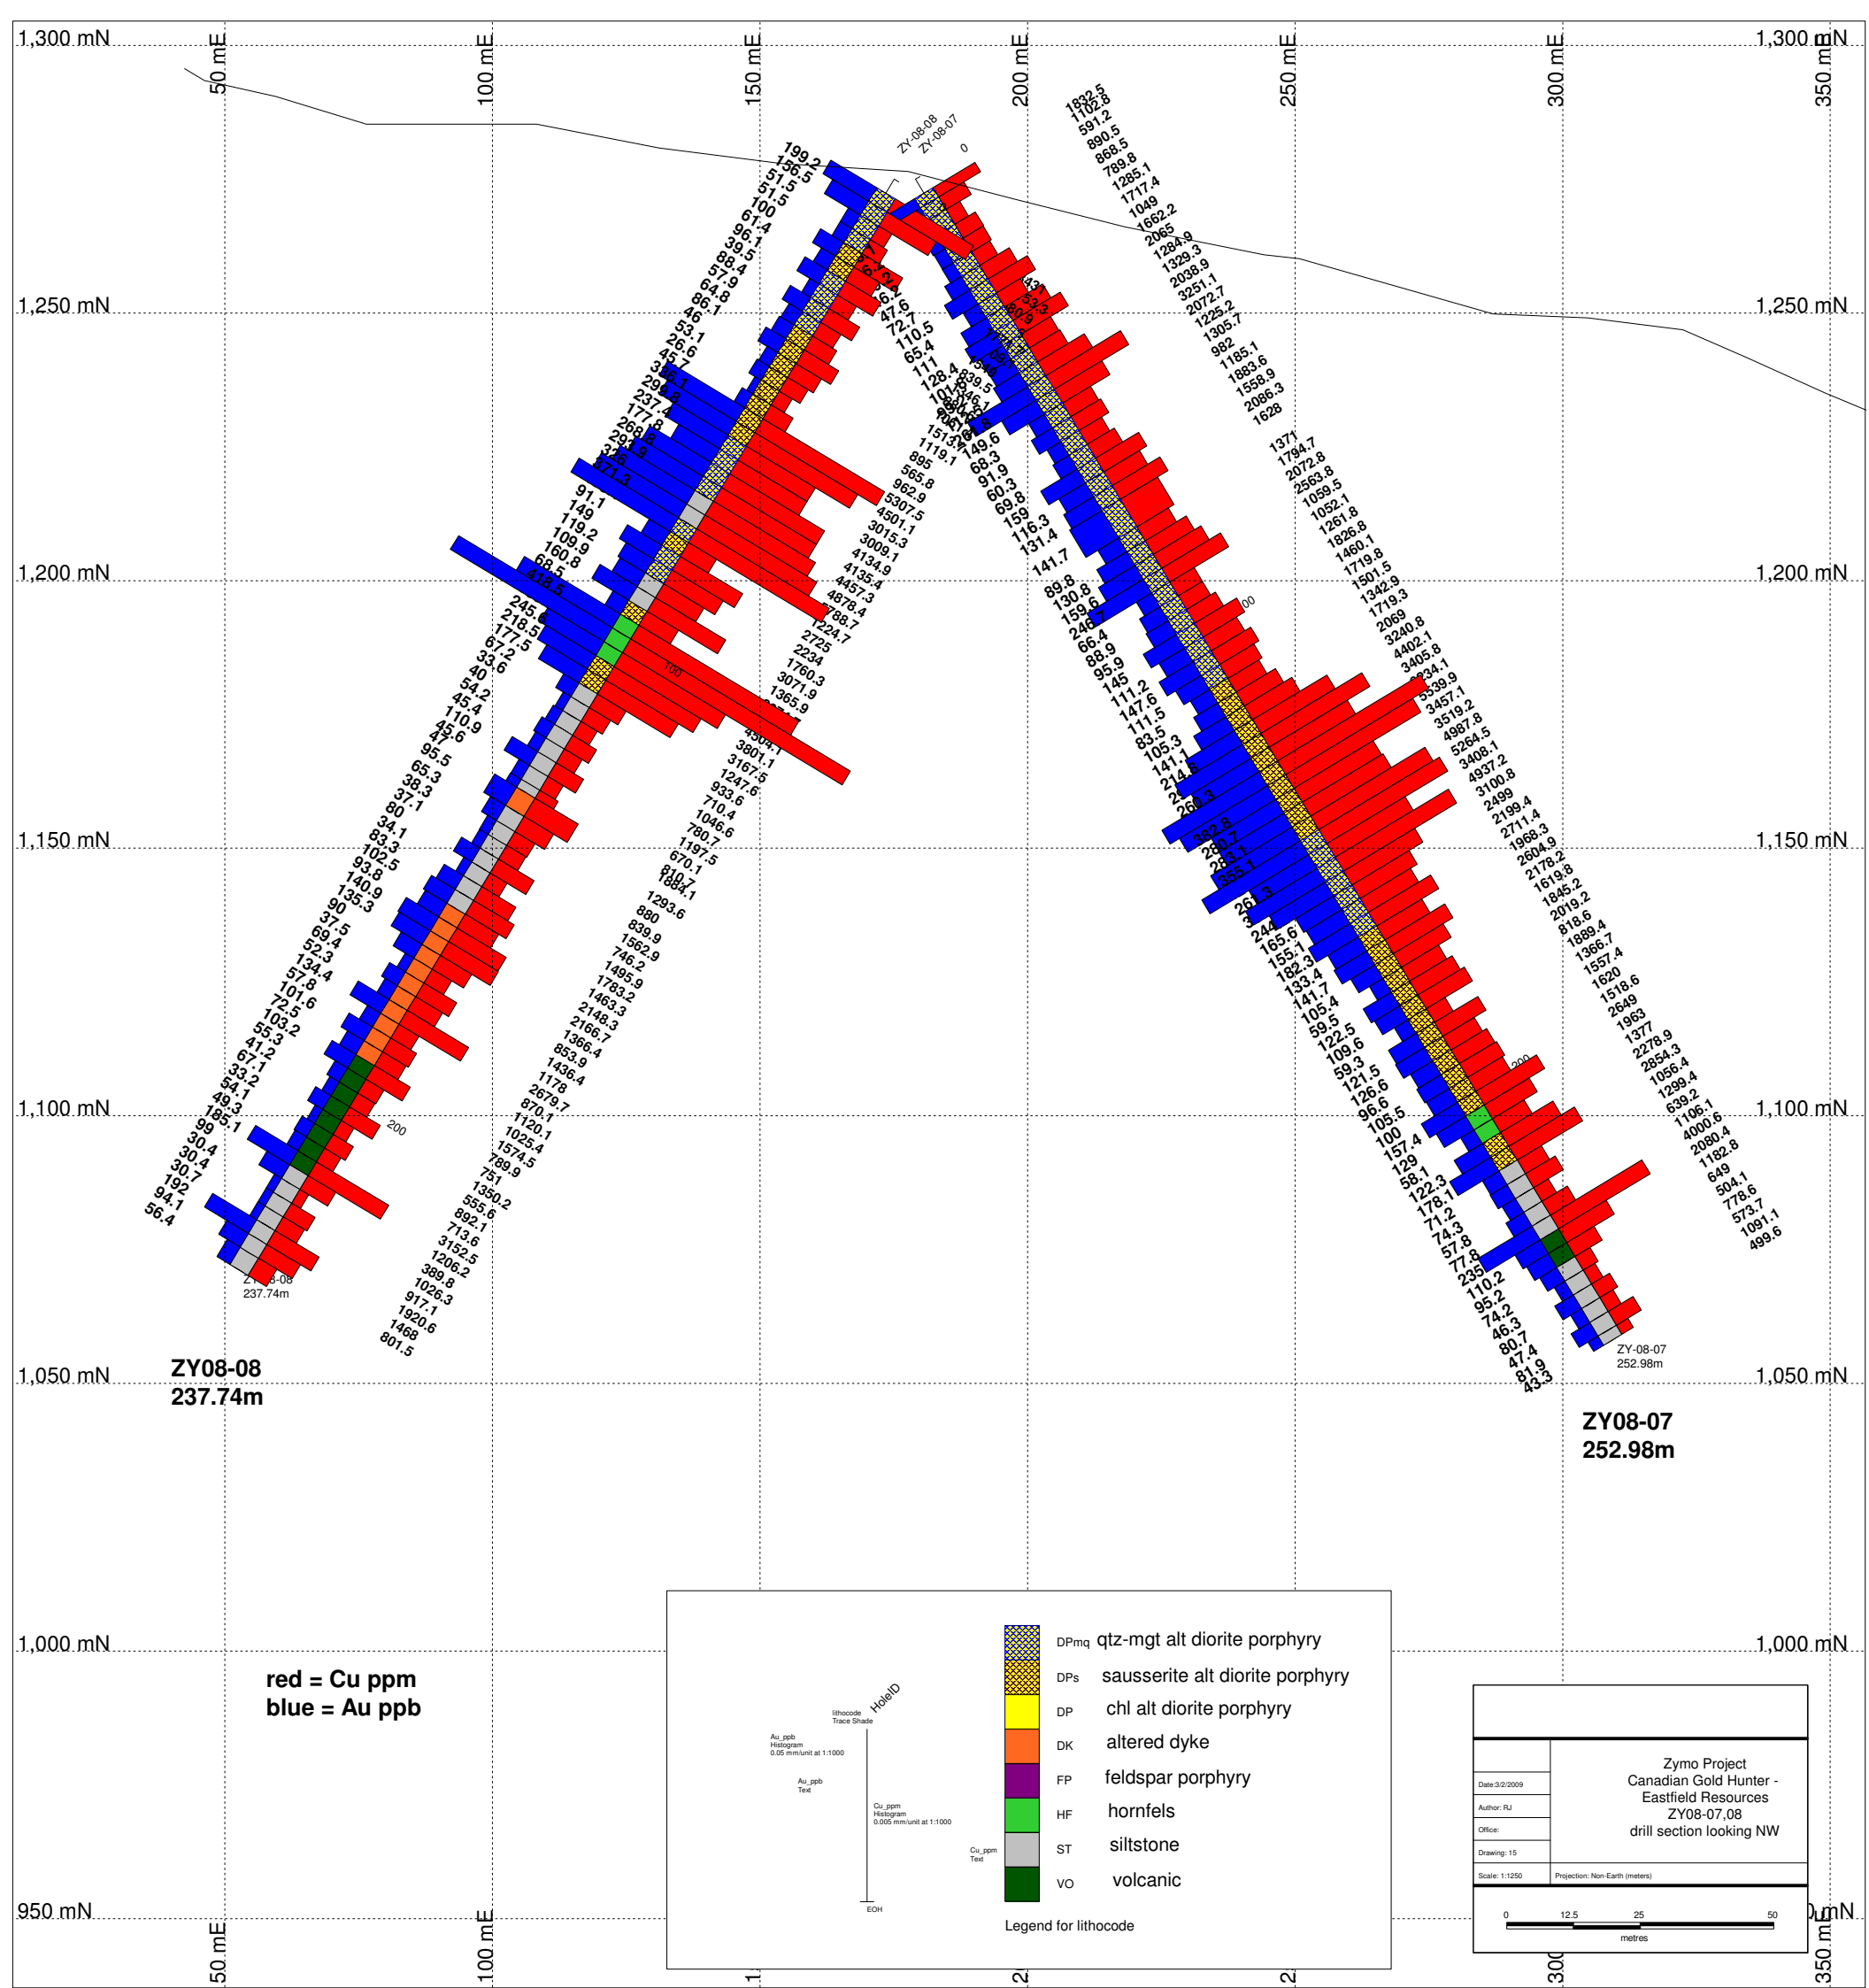

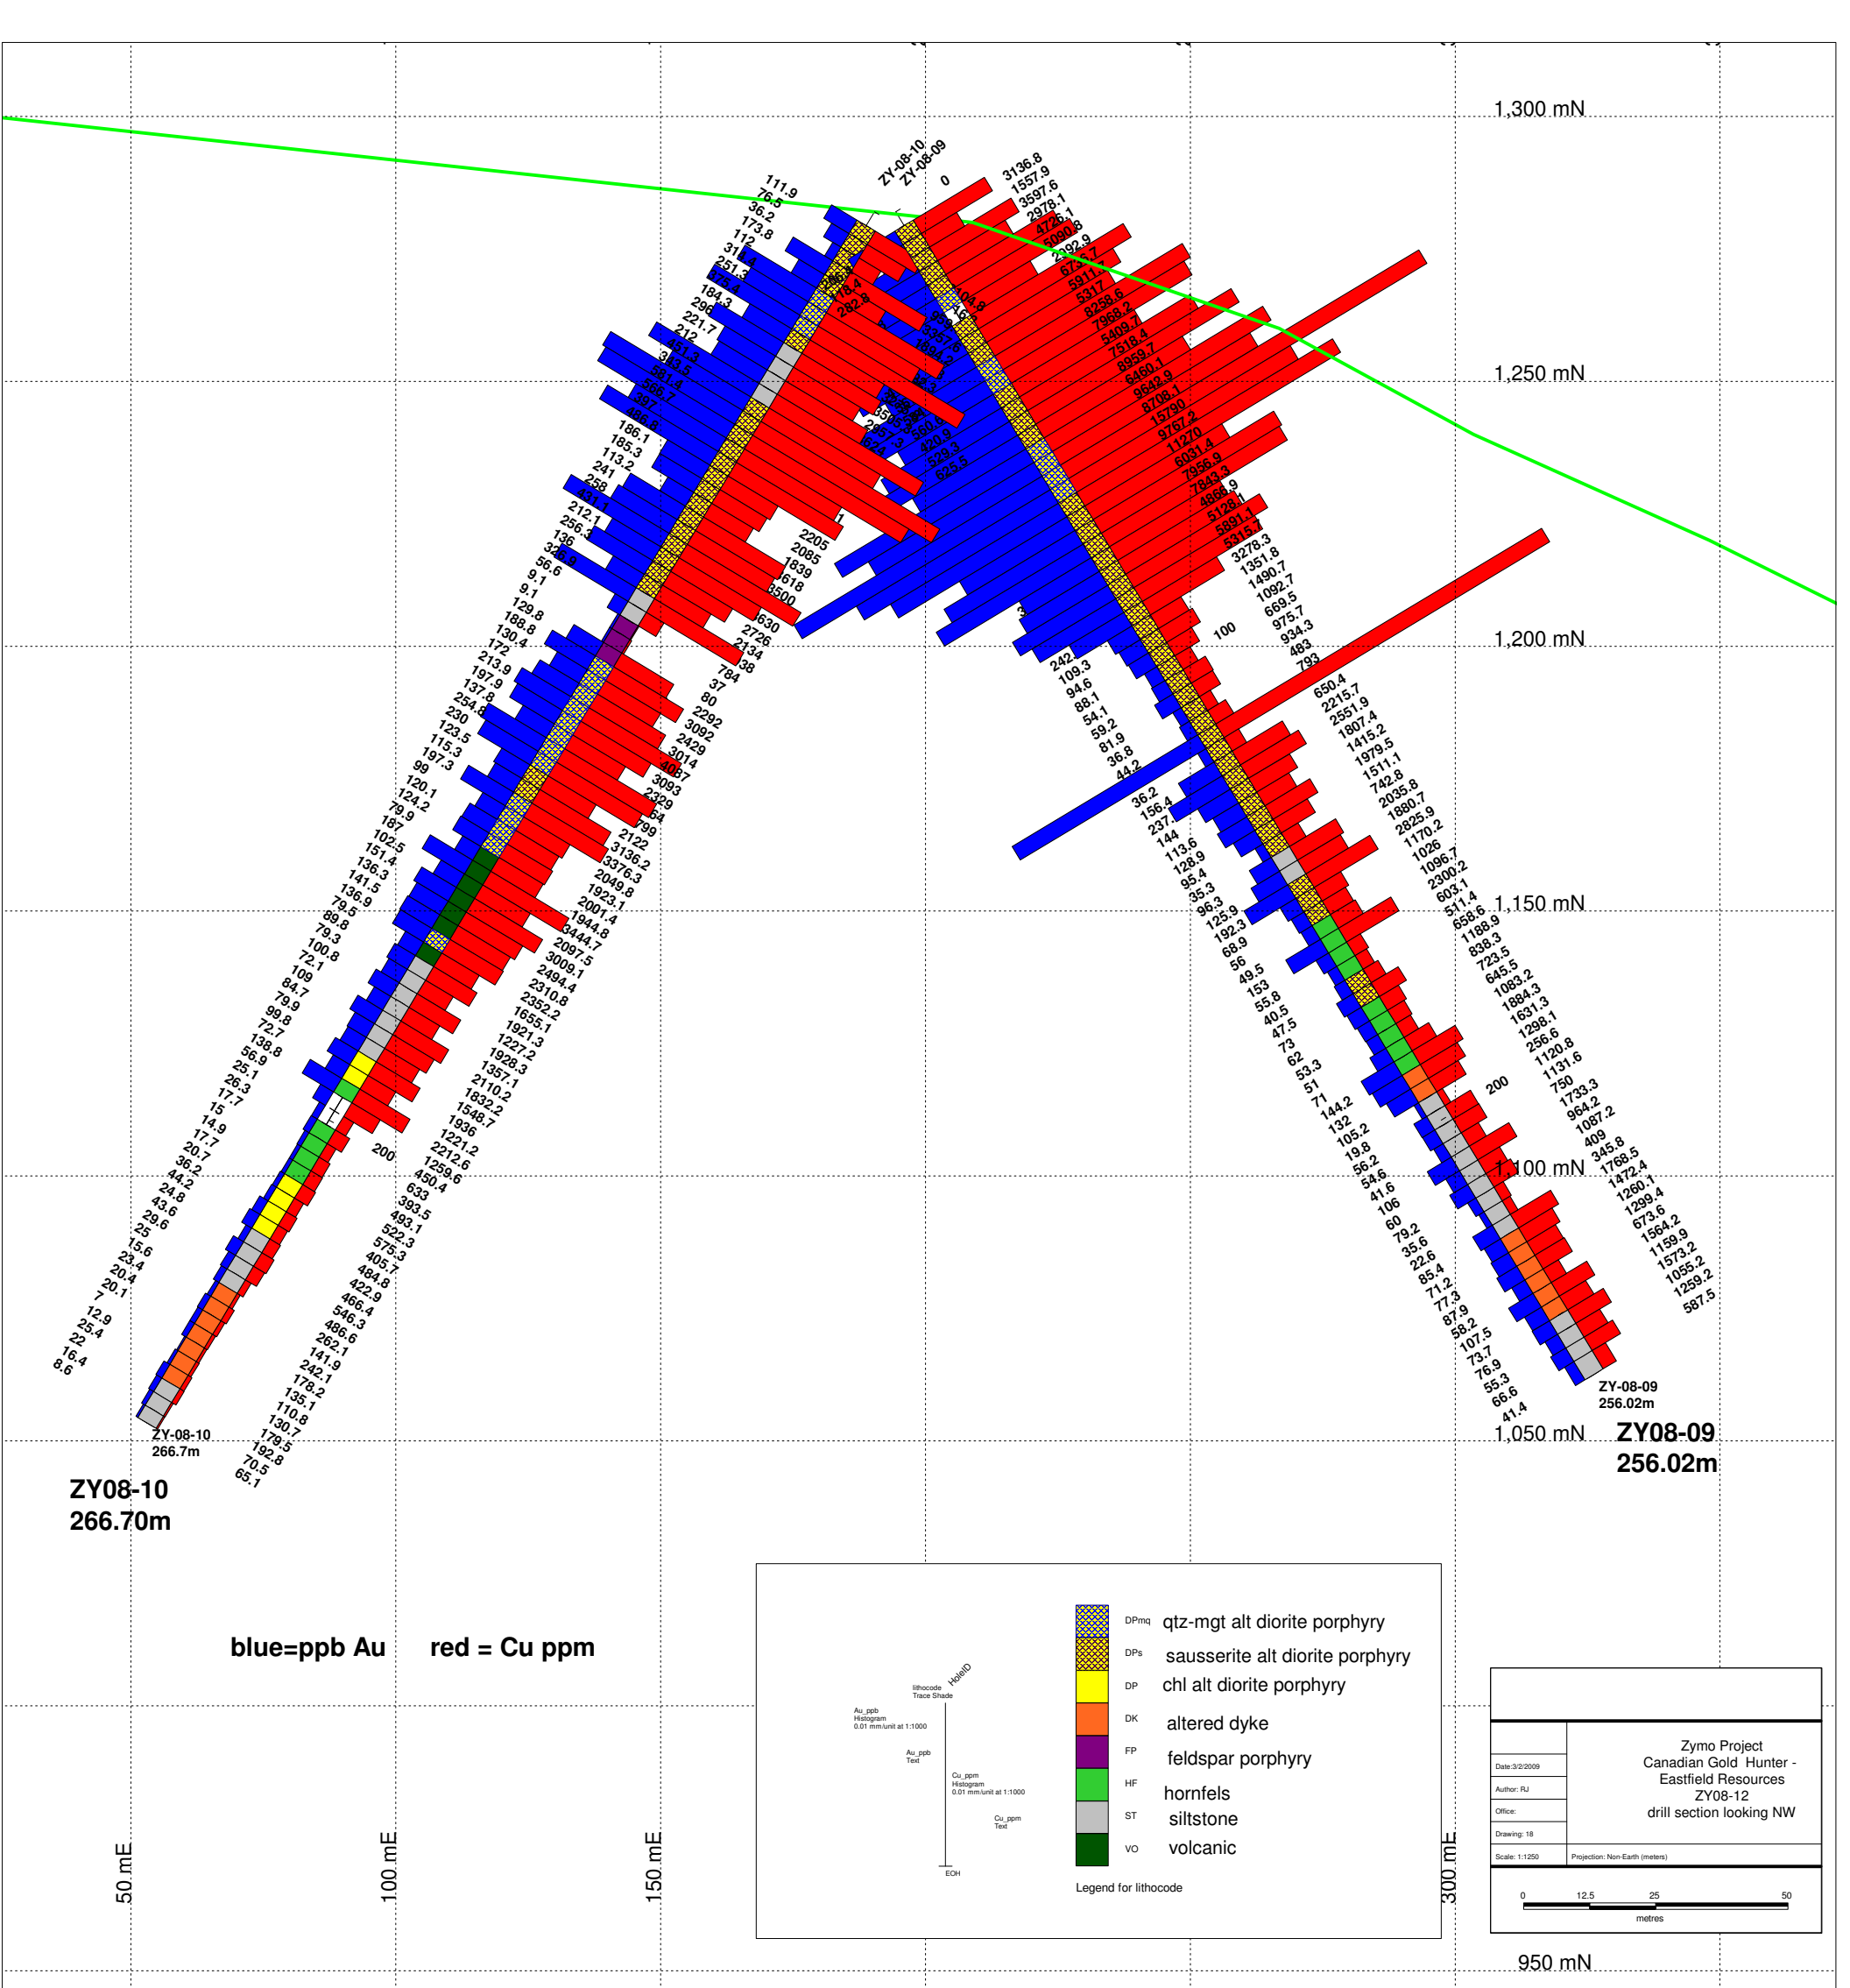


Zymo Project Canadian Gold Hunter - Eastfield Resources ZY08-12 drill section looking NW	
Date: 3/2/2009	
Author: RJ	
Office:	
Drawing: 18	
Scale: 1:250	Projection: Non-Earth (meters)

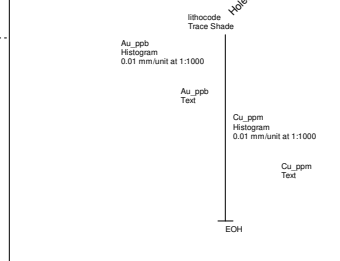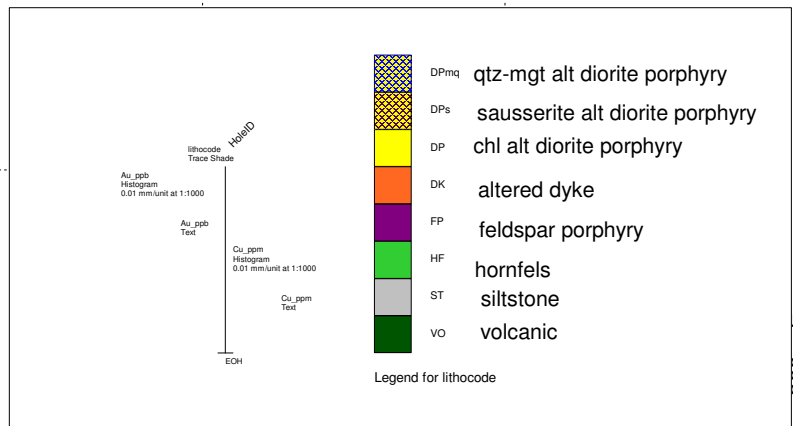

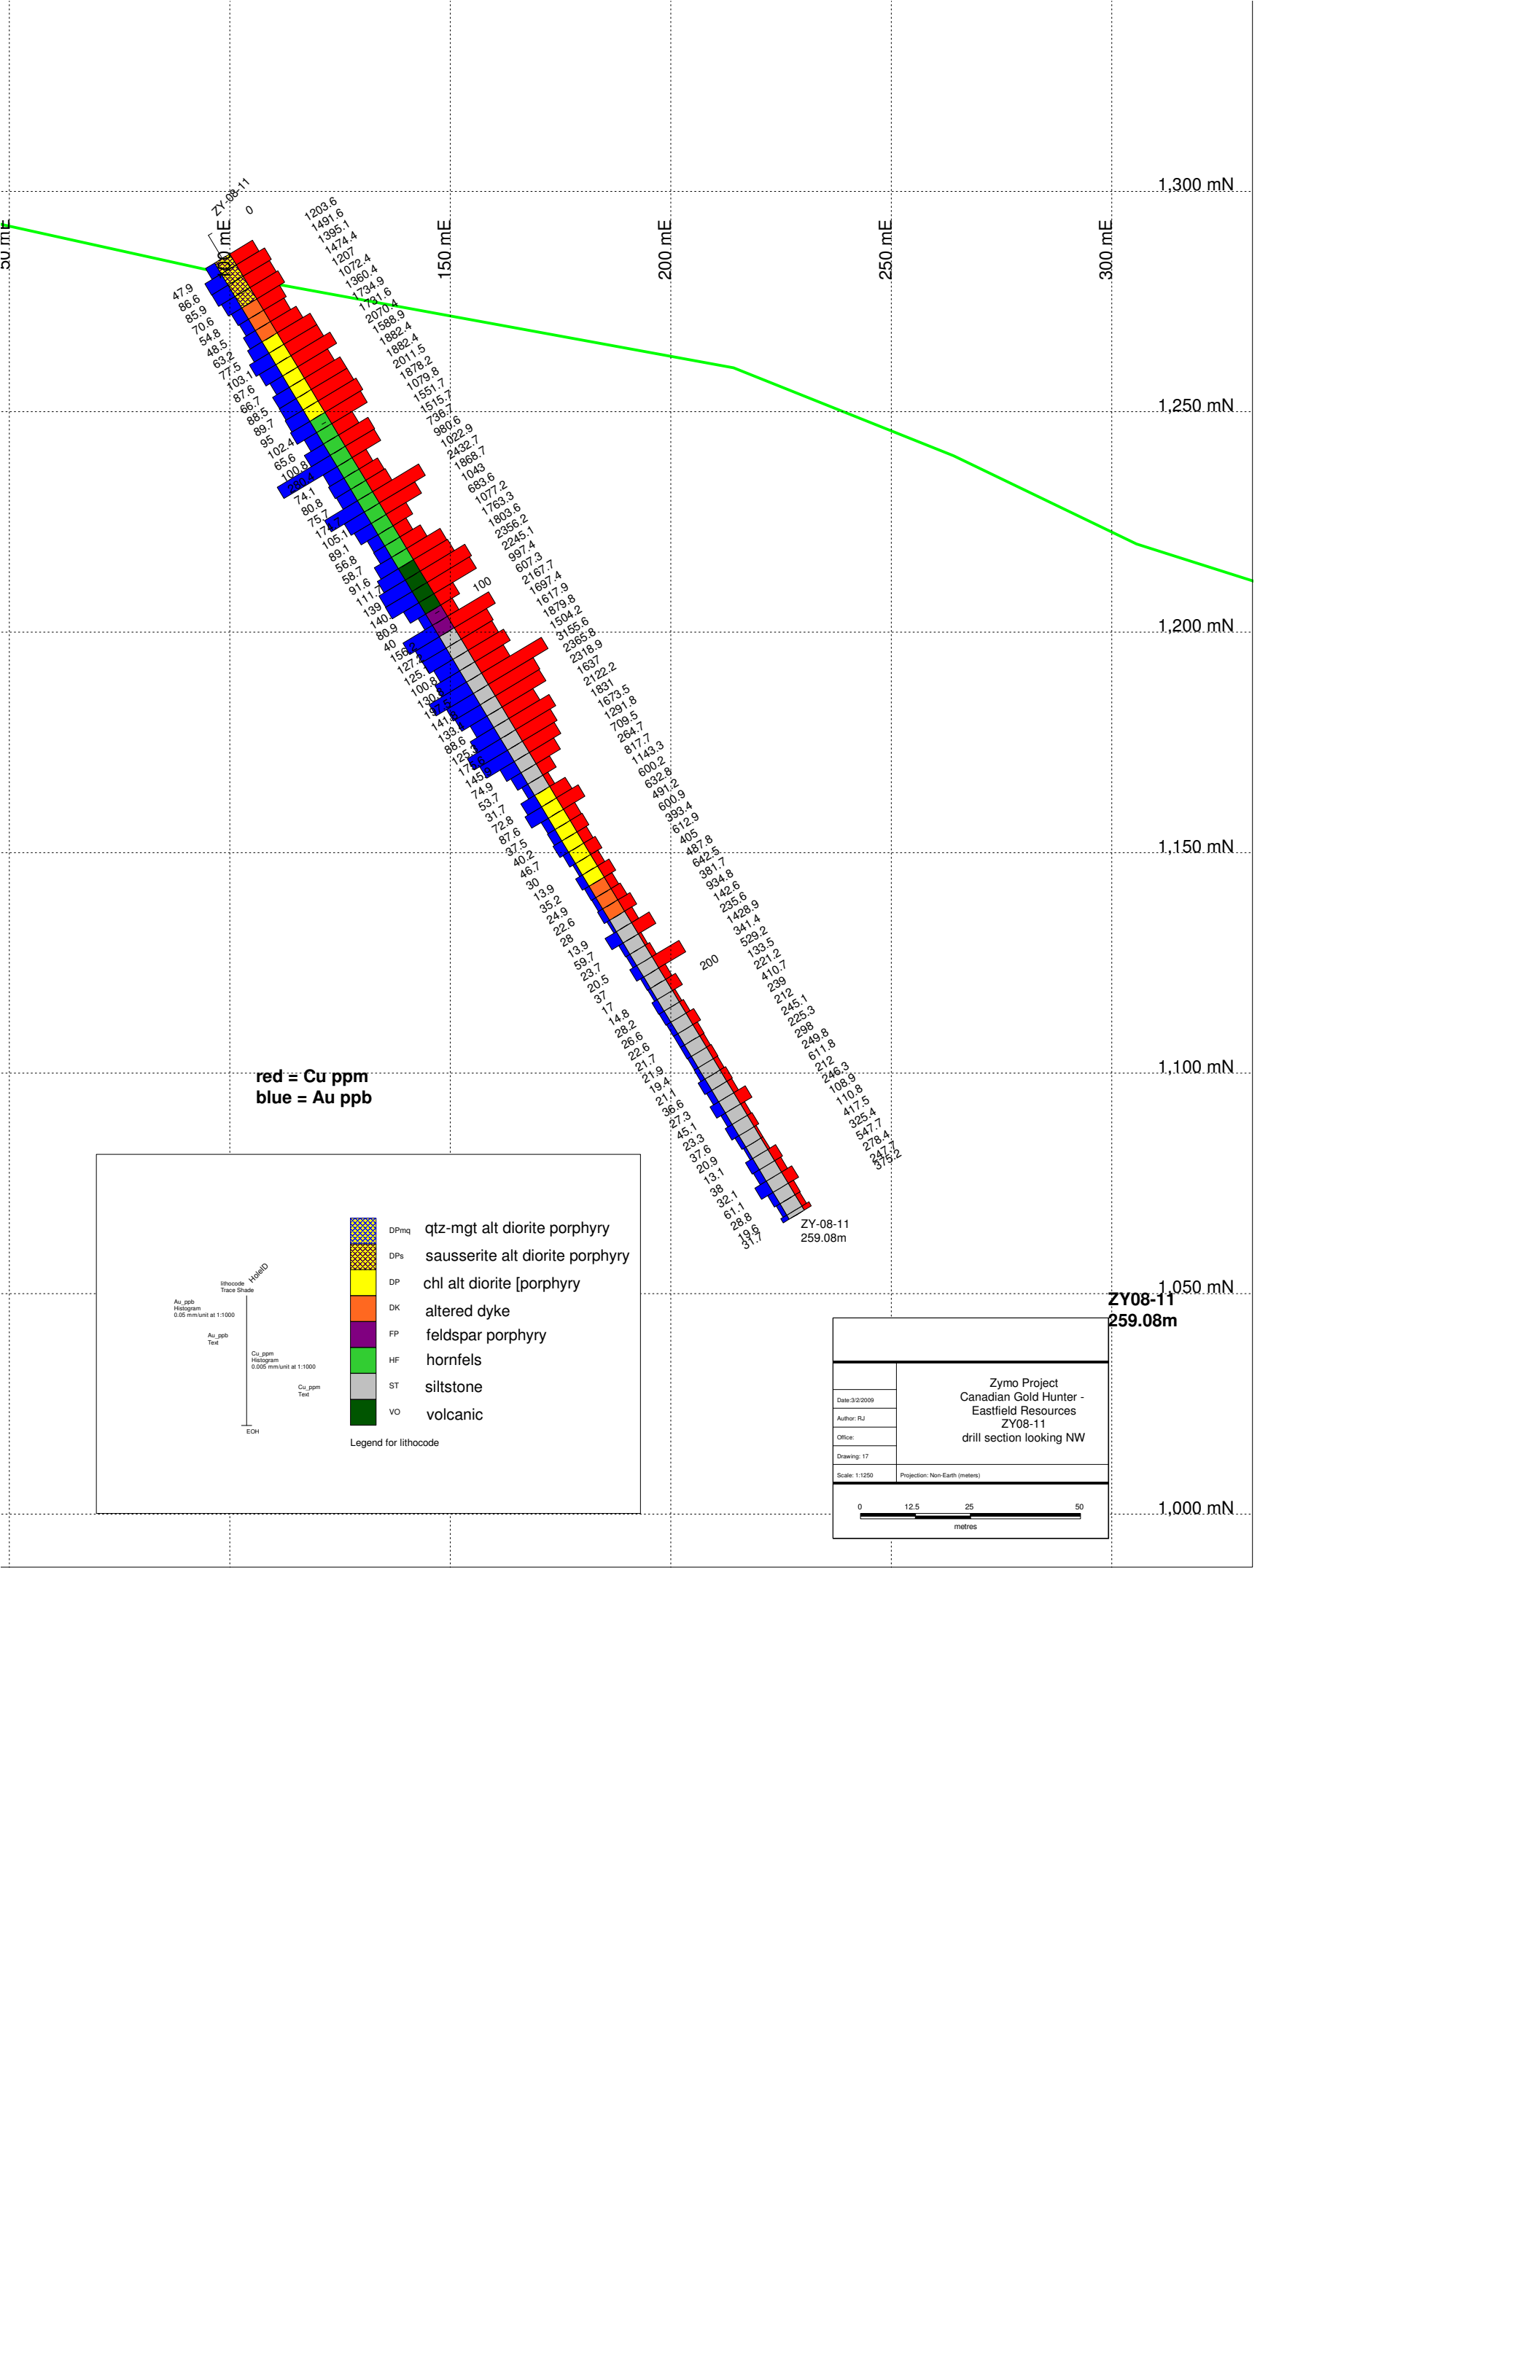


red = Cu ppm
blue = Au ppb

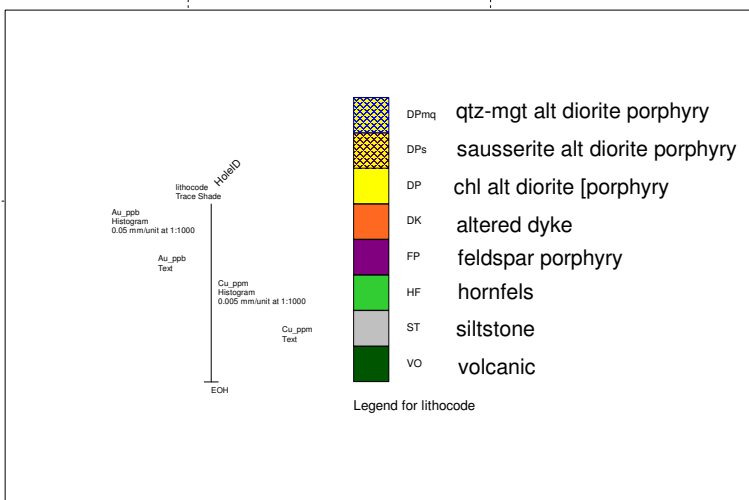

Zymo Project Canadian Gold Hunter - Eastfield Resources ZY08-11 drill section looking NW	
Date: 3/2/2009	
Author: RJ	
Office:	
Drawing: 17	
Scale: 1:1250	Projection: Non Earth (meters)

ZY08-11
259.08m

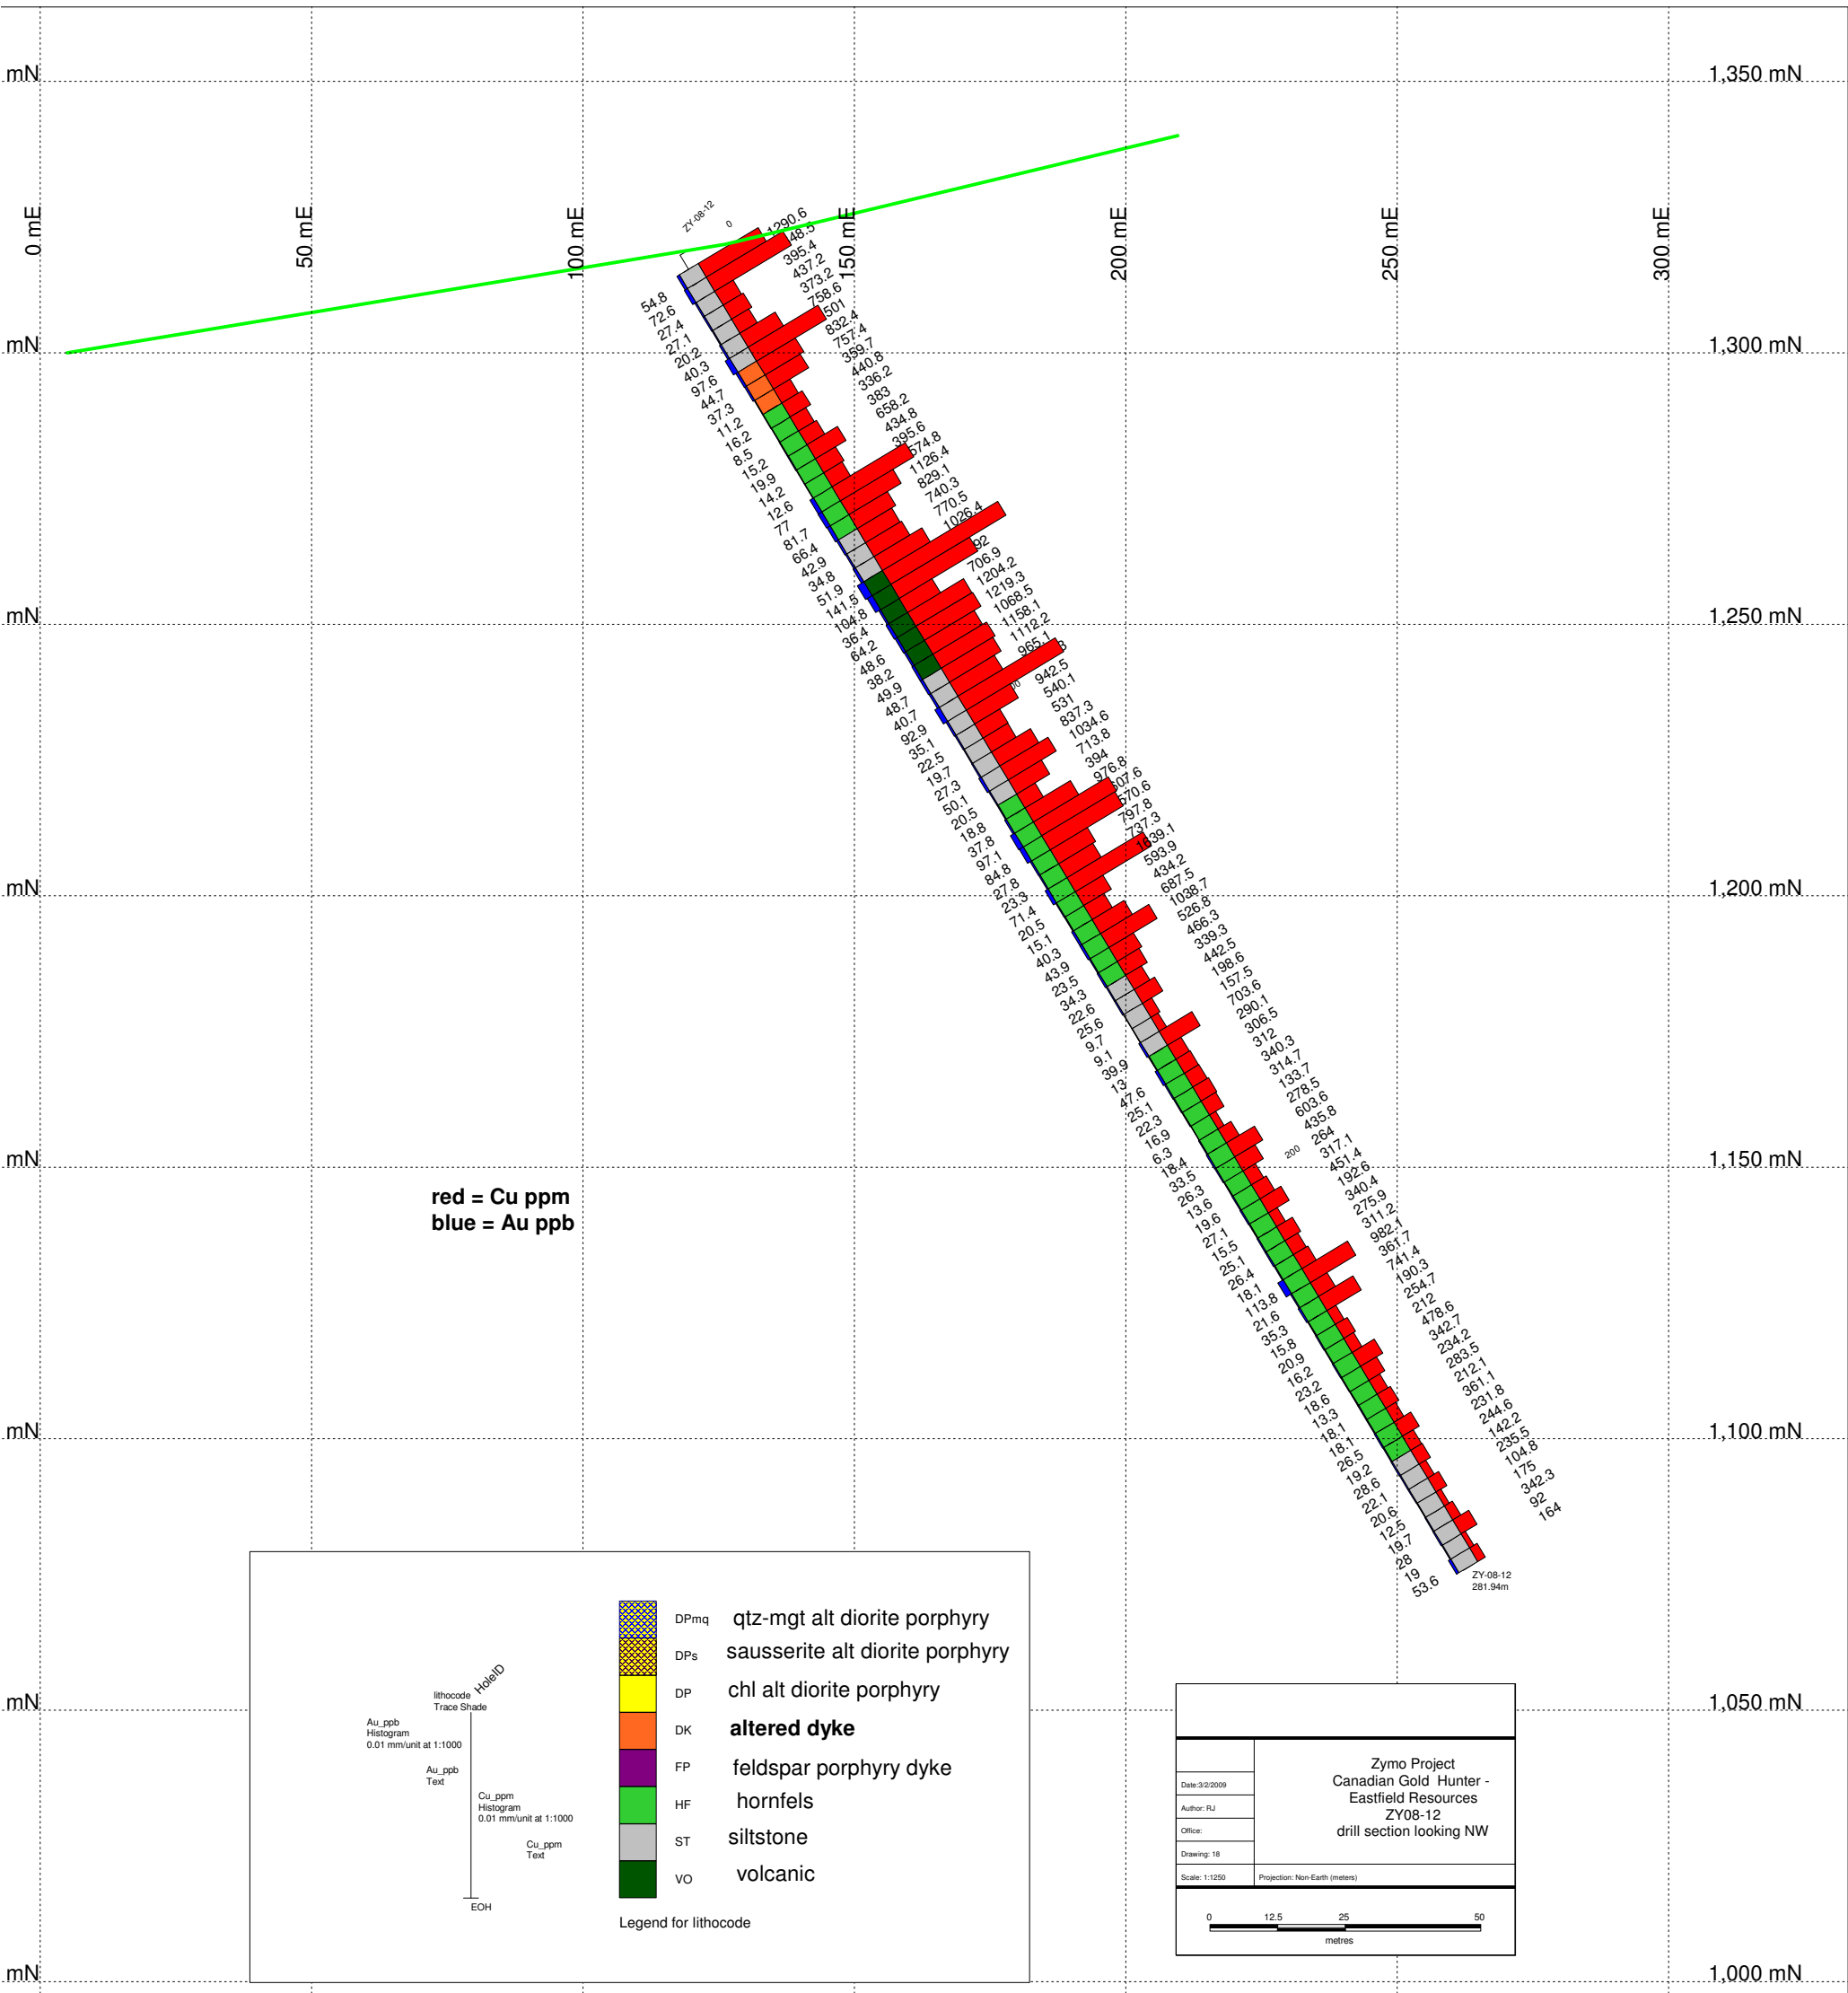

	DPmq	qtz-mgt alt diorite porphyry
	DPs	sausserite alt diorite porphyry
	DP	chl alt diorite porphyry
	DK	altered dyke
	FP	feldspar porphyry dyke
	HF	hornfels
	ST	siltstone
	VO	volcanic

Legend for lithocode

Au_ppb Histogram 0.01 mm/unit at 1:1000
 Au_ppb Text
 Cu_ppm Histogram 0.01 mm/unit at 1:1000
 Cu_ppm Text
 EOH
 Holoand
 lithocode Trace Shade