

Event # 4252312

**2008 DIAMOND DRILLING ASSESSMENT REPORT ON THE
RECORD RIDGE SOUTH PROPERTY**

(FRANK SR. 3 & HIDDEN VALLEY 3 CLAIMS)

ROSSLAND, BC

TRAIL CREEK MINING DIVISION

LATITUDE: 49° 2' 54"N

LONGITUDE: 117° 52' 50"W

NTS MAP SHEET 082F 004

BC Geological Survey
Assessment Report
30647



PREPARED FOR:

WEST HIGH YIELD RESOURCES LTD.

P.O. BOX 68121, CALGARY, AB

BY:

Hun Kim, P.Ge

Cory Peck, B.Sc.

January 28, 2009

TABLE OF CONTENTS

	Page
1. SUMMARY	5
2. INTRODUCTION, TERMS OF REFERENCE AND DISCLAIMER	8
3. PROPERTIES, LOCATION AND DESCRIPTION	9
3.1 Property Location	9
3.2 Property Description	10
4. ACCESSIBILITY, CLIMATE, LOCAL RESOURCES	12
INFRASTRUCTURE & PHYIOGRAPHY	12
4.1 Accessibility	12
4.2 Climate	12
4.3 Local Resources & Infrastructure	12
4.4 Physiography	12
5. HISTORY	13
5.1 General History of the Rossland District	13
5.2 History of Record Ridge South Property	13
6. GEOLOGICAL SETTING	15
6.1 Regional Setting	15
6.2 Regional Structure	18
7. LOCAL GEOLOGY	19
7.1 Occurrences of the Ultramafic Rocks in Rossland Area	19
7.2 Lithology of the Record Ridge Ultramafic Body	22
7.2.1 Ultramafics	22
7.2.2 Thickness of Ultramafic Rocks	24
7.2.3 Volcanic, Sub-volcanic and Intrusive Rocks	25
8. MINERALIZATION	29
8.1 Magnesium & Nickel	29
8.2 Cobalt	32
8.3 Chromium	32
8.4 Base Metal and Precious Metal Occurrences	33
8.4.1 Base Metal Showings	33
8.4.2 Chromite Showings	34
8.4.3 Precious Metal Showings	34
8.5 Platinum Group Elements	34

9. EXPLORATION	35
10. DRILLING	36
10.1 Introduction	36
10.2 Drill Results	38
10.3 Geotechnical Logging	41
11. SAMPLING METHODS AND ANALYSES	41
12. DATA VERIFICATION	42
13. MINERAL PROCESSING AND METALLURGICAL TESTING	42
14. MINERAL RESOURCE AND MINERAL RESERVE ESTIMATES	43
15. INTERPRETATION AND CONCLUSION	43
16. RECOMMENDATIONS	44
17. STATEMENT OF COSTS	45
18. REFERENCES	46
19. STATEMENT OF QUALIFICATION	47

APPENDIX I Drilling results of 45 drill holes (geological core logs)
with grade compilation –Ni, Co, Mg, Cr, also selectively for Au, Ag and Pt.
***Entire suite of drill logs can be found in attached file in digital format.

APPENDIX II 2008 assay File

APPENDIX III Two Metallurgical Test Reports by Met-Solve Laboratories Inc.
Magnesium Recovery from WHY Resources' samples
(September 17, 2008 & October 28, 2008)

APPENDIX IV Petrographic Analysis Reports of the Record Ridge ultramafics

LIST OF FIGURES:

	Page
Figure 1 Location Map	7
Figure 2 2007 Drill Program Index and Drill Location Plan	9
Figure 3 Claim Map & Topography	11
Figure 4 Distribution of Ultramafic Intrusion in the Cordilleran Orogen, B.C, Yukon Territory and Southeast Alaska	16
Figure 5 Regional Geology of Rossland Area	17
Figure 6 Regional Cross-Section	18
Figure 7A Geological Setting of Record Ridge South Magnesium Deposit	20
Figure 7B Legend for Figure 7A	21
Figure 8 Local Geology (adapted from GSC Bulletin 108)	23
Figure 9 Isopach Plan of Mg-Ni-Co Bearing Serpentinite Thickness (Fully diluted with intervened sub-volcanic and intrusive dykes)	25
Figure 10 2008 Drill Program Line Grid Geology (Record Ridge South Magnesium Deposit)	26
Figure 11 Generalized Geological Profile (N-S Cross Section Line 1175 W)	27
Figure 12 Generalized Geological Profile (N-S Cross Section Line 1225 W)	28
Figure 13 Generalized Geological Profile (N-S Cross Section Line 1275 W)	29
Figure 14 Generalized Geological Profile (N-S Cross Section Line 1125 W)	29

1. SUMMARY

- The Record Ridge South Magnesium Deposit situated 11 kilometres southwest of Rossland, BC is mainly underlain by the ultramafic rocks previously known as “Rossland ultramafic body” (Open File 1990-27) or “Record Ridge ultramafic body”, which is rhombic in shape with an area of about 6.2 square kilometers (British Columbia Geological Survey Bulletin 108).
- In 2007 Diamond Drilling Assessment Report of the Ivanhoe Ridge Property, the authors proposed to use the name of “Ivanhoe Ridge ultramafic body” for the “Record Ridge ultramafic body”, based on the rock occurrences in the Record Ridge, which is mainly underlain by Marron Formation of Eocene comprising volcanic and sub-volcanic rocks and Coryell intrusions consisting of syenite, monzonite and granite. Although the authors proposed to use the name of “Ivanhoe Ridge ultramafic body” in 2007, the name of “Record Ridge ultramafic body” remains unchanged in this report to be consistent with the existing Geological Survey Bulletin 108.
- In the entire field season of 2008, the central section of the Record Ridge ultramafic body was tested by line-grid geological mapping, sampling and diamond drilling to assess an economic potential of the magnesium-rich nickeliferous cobalt-chromite bearing serpentinites. West High Yield (W.H.Y) Resources has spent \$1,562,626 for the 2008 diamond drill program on the Record Ridge South property
- In 2008, 45 vertical NQ diamond drill holes totaling 5,279 meters were drilled on a 50-metre square grid pattern within an approximate 200 m x 500 m section for a NI 43-101 mineral resource estimate in the central portion of the Record Ridge South ultramafic body (**Fig. 2**). The technical report for a NI 43-101 mineral resource estimation of the Record Ridge South Magnesium Deposit is being independently prepared by SRK Consulting Engineers & Scientists (Bart Stryhas, Ph.D), *7175 West Jefferson Avenue Suite 3000 Lakewood, Colorado 80235 USA*.
- The 2008 drill program included 3,330 drill core samples for ICP-AES analyses of 24 elements including magnesium, nickel, cobalt and chromium. Also on the selected drill core samples, atomic absorption and fusion analyses were tested for precious metals including gold, silver, platinum, cadmium and base metals.
- The Record Ridge ultramafic rocks host a significant magnesium mineralization of economic interest. Ultramafic rocks are characterized by high magnesium weight percent (wt %). In overall the property, magnesium values are averaged to be 24.5 wt % Mg or 40.63 wt % of MgO.
- The Record Ridge ultramafics contain also other metals of economic interest. The nickel values in the ultramafics are averaging 0.20 % Ni. The cobalt and chromium values are averaging 106 ppm Co and 0.33 % Cr, respectively.

- The 2008 line-grid drill program for a resource estimation can be divided into two sectors (northern and southern) by an east-west trending fault on line 350S **(Figs. 2 & 10)** The southern sector of resource definition drilling tested by 24 holes gave positive values of magnesium (24 % Mg) over widths from surface, ranging from 11 to 122.2 metres and averaging 40 metres. Contrastingly, the northern sector tested by 21 holes returned high values of magnesium averaging 25.1 % Mg with broad zones of ultramafic rocks from surface or near surface, ranging from 36.5 metres to 148.2 metres and averaging 100 meters. This wide zone of the magnesium rich serpentinite is open to the west.
- Two metallurgical testing for magnesium extraction were conducted by Met-Solve Laboratories Inc. (www.met-solve.com), 8815 Eastlake Drive, Burnaby, BC V5A 4T7. Met-Solve's initial metallurgical testing of the 12 kilograms of drill cores gave the best results with 84.5% extraction of the magnesium into solution using sulphuric acid(H_2SO_4) leaching at 70 °C to produce magnesium sulphate ($MgSO_4$) into solution. Encouraged by the results of magnesium recovery from the initial testing, West High Yield Resources shipped an additional 200 kilograms of drill cores to Met-Solve Lab. for final metallurgical testing. Met-Solve's final metallurgical testing, using hydrochloric acid (HCl) leaching method, resulted in extraction of 78.6 % of the magnesium in the form of magnesium chloride($MgCl_2$) into solution.
- In addition to metallurgical testing, thin sections of 12 drill core samples were petrographically analyzed. The results of petrographical works are summarized in the report.
- The Record Ridge South Magnesium Deposit warrants additional exploratory works. Continuous from the 2008 drill sites (northern sector of resource estimation), 2009 drilling should be moved progressively westward on a 50-metre square grid pattern.



FIGURE 1 - LOCATION MAP

2. INTRODUCTION, TERMS OF REFERENCE AND DISCLAIMER

This report summarizes a geological assessment on the Frank Sr. 3 and Hidden Valley claim group, 11 kilometers southeast of Rossland, BC, based on the results of the 2008 diamond drilling program in Trail Creek Mining Division. This report is submitted as assessment work in compliance with requirements of National Instrument 43-101 and Form 43-101F1 in order to maintain the Record Ridge South property (Frank Sr. 3 and Hidden Valley claims) and its northerly contiguous entire mineral claims held by West High Yield (W.H.Y.) Resources Ltd., P.O. Box 68121, Calgary, Alberta. West High Yield (W.H.Y) Resources has spent **\$1,562,626** for the 2008 diamond drill program on the Record Ridge South property.

The author, H. Kim, P.Geo/P.Eng. is a Qualified Person as defined by National Instrument 43-101. He has planned, supervised and directly participated in all field programs on the Record Ridge South property. Cory Peck, B.Sc, G. I. T. has conducted the surface sampling of the ultramafics, reconnaissance mapping and line-grid outcrop mapping in the selected area and specific gravity measurements of all drill cores of the Record Ridge South Magnesium Deposit.

The portion of regional geology in this report is primarily based on published reports (Geological Survey of Canada and Geological Survey of BC) and private reports available to the author. All consulted sources are listed in the References section.

The Crown granted lots and land titles of 8 crown granted claims held by West High Yield Resources were transferred from technical report (NI 43-101) by B. Price, P. Geo. (January 5, 2006).

Units of measure are metric and all currency is reported in Canadian dollars. Grade values for nickel and cobalt, precious metals (Au, Ag, Pt, Pl, etc) are reported in g/t and in percent for magnesium and chromium.

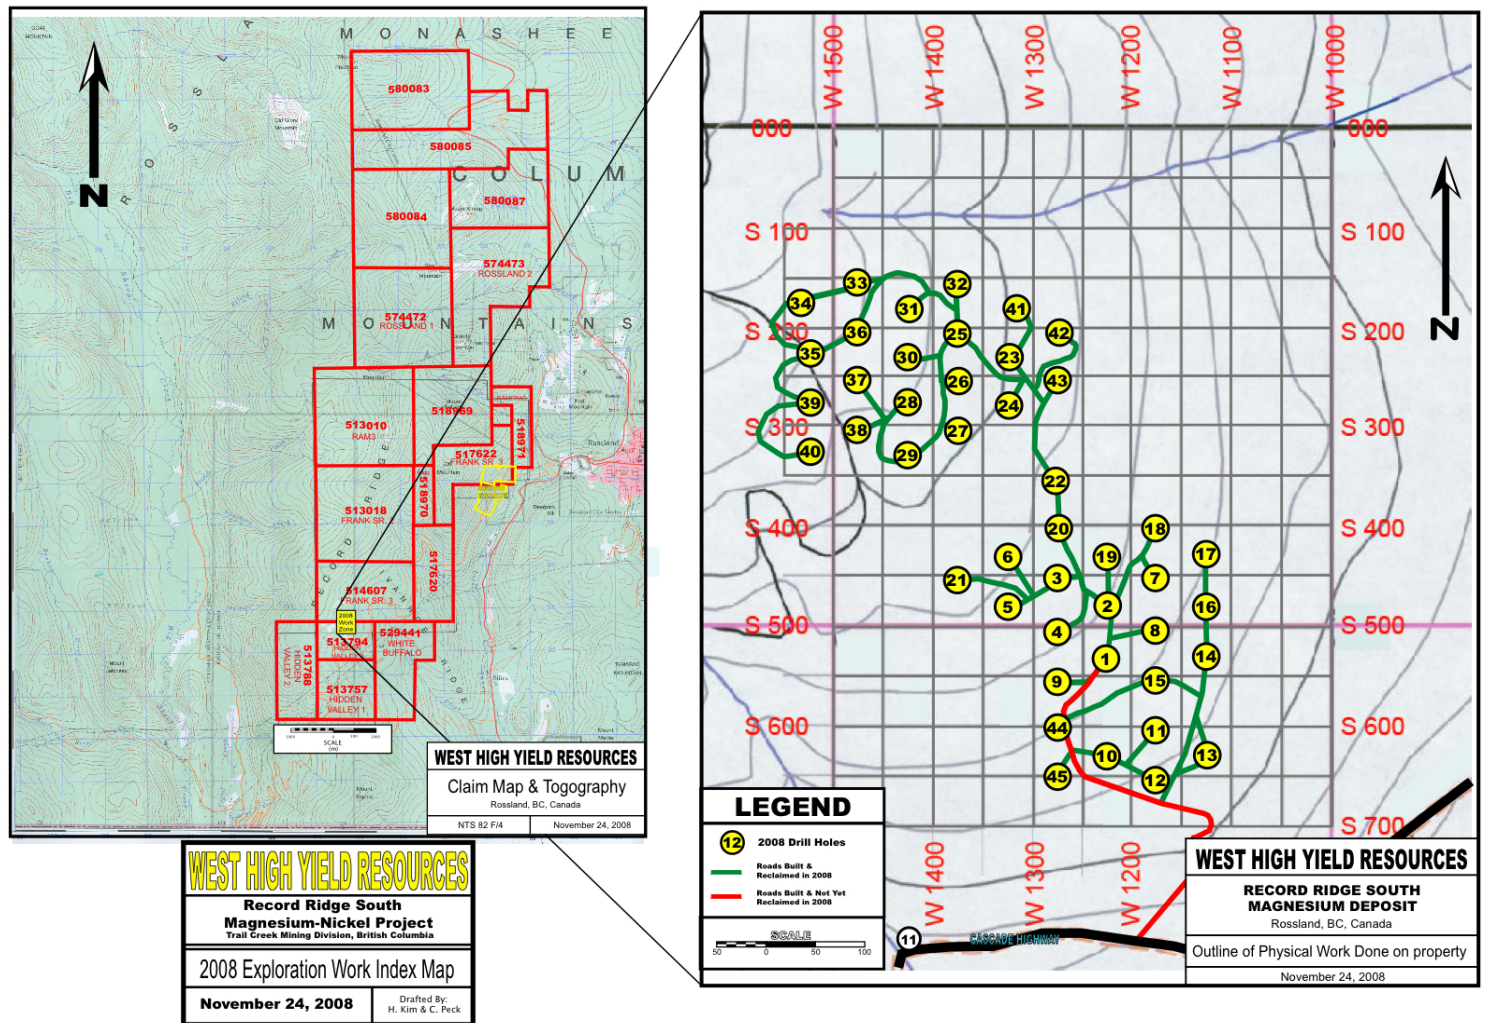


FIGURE 2 - 2008 DRILL PROGRAM INDEX MAP & DRILL LOCATION PLAN

3. PROPERTY LOCATION & DESCRIPTION

3.1 Property Location (Figures 1 and 2)

The Record Ridge South property lies 11 kilometers southwest of the town of Rossland in Trail Creek Mining Division of southeastern British Columbia and about 400 km east of Vancouver and 8 km north of the Canada-USA border. The subject property for this report (Frank Sr. 3 and Hidden Valley claims) covers an area of 763 hectares between latitudes 49° 2' North and longitudes 117° 53' West in NTS Maps Sheet 082F.

3.2 Property Description

The configuration of the mineral claims is illustrated on **Figure 3** (BC Mineral Titles Reference Map 82F) and details are presented in the following table:

CLAIMS DESCRIPTION

Division	Tenure Number	Claim Name	Date of Record	Expiry Date	Status	Area (Hectares)
Claims on which 2008 drilling took place.	514607	Frank SR 3	2006/June/16	2018/Feb/28	Good	317.575
	513794	Hidden Valley 3	2005/ June/02	2018/Feb/28	Good	127.057
Cell claims Contiguous with Frank SR. 3 (514607) & Hidden Valley 3 (513794)	513018	Frank SR 2	2007 /May/19	2018/Feb/28	Good	529.112
	513010	RAM 3	2007 /May /19	2018/Feb/28	Good	528.872
	518969	No name	2006 /Sep / 12	2018/Feb/28	Good	359.616
	518970	RAM	2006 /Aug / 12	2018/Feb/28	Good	64.488
	517622	Frank SR 3	2006 /Jul / 13	2018/Feb/28	Good	232.764
	518971	RAMFRAC	2006 /Aug / 12	2018/Feb/28	Good	105.782
	517620	No name	2006 /Sep /24	2018/Feb/28	Good	211.698
	513794	Hidden Valley	2005 /June /01	2018/Feb/28	Good	190.626
	513788	Hidden Valley 2	2005 /Jun /02	2018/Feb/28	Good	211.789
	529441	White Buffalo	2006 /Mar /05	2018/Feb/28	Good	254.141
	574472	Rossland 1	2008 /Jan /25	2009/Jan/25	Good	528.645
	574473	Rossland 2	2008 /Jan /25	2009/Jan/25	Good	528.576
	580083	West High Yield	2008/Apr /01	2009/Apr/1	Good	507.034
	580084	West High Yield	2008 /Apr /01	2009/Apr/1	Good	528.435
	580085	West High Yield	2008/ Apr /01	2009/Apr/1	Good	528.265
	580087	West High Yield	2008 /Apr /01	2009/Apr/1	Good	359.307
Crown granted claims, contiguous with Frank SR 3 (517622) & RAMFRAC (518971)	Lot	Claim name	Title Subsurface Rights	C.G	Equity	Area Hectares
	1186	Midnight	1134921	87-80	100%	17.66
	1216	June	N.A.	156-86	100%	17.40
	1217	Golden Butterfly	N.A.	200.90	100%	17.40
	1943	Golden Butterfly Fr.	N.A.	237-90	100%	4.57
	1215	Little Dalles	KV110354	278-87	100%	2.73
	2675	OK Fraction	N.A.	274.90	100%	0.49
	678	OK	KV112056	60-68	51%	12.85
	679	IXL	KV112053	60-68	100%	7.85
	Plan S82	Sub Lot 82	KV112055	87-80	51%	4.98
	539	Golden Drip	N.A.	N.A.	N.A.	N.A.

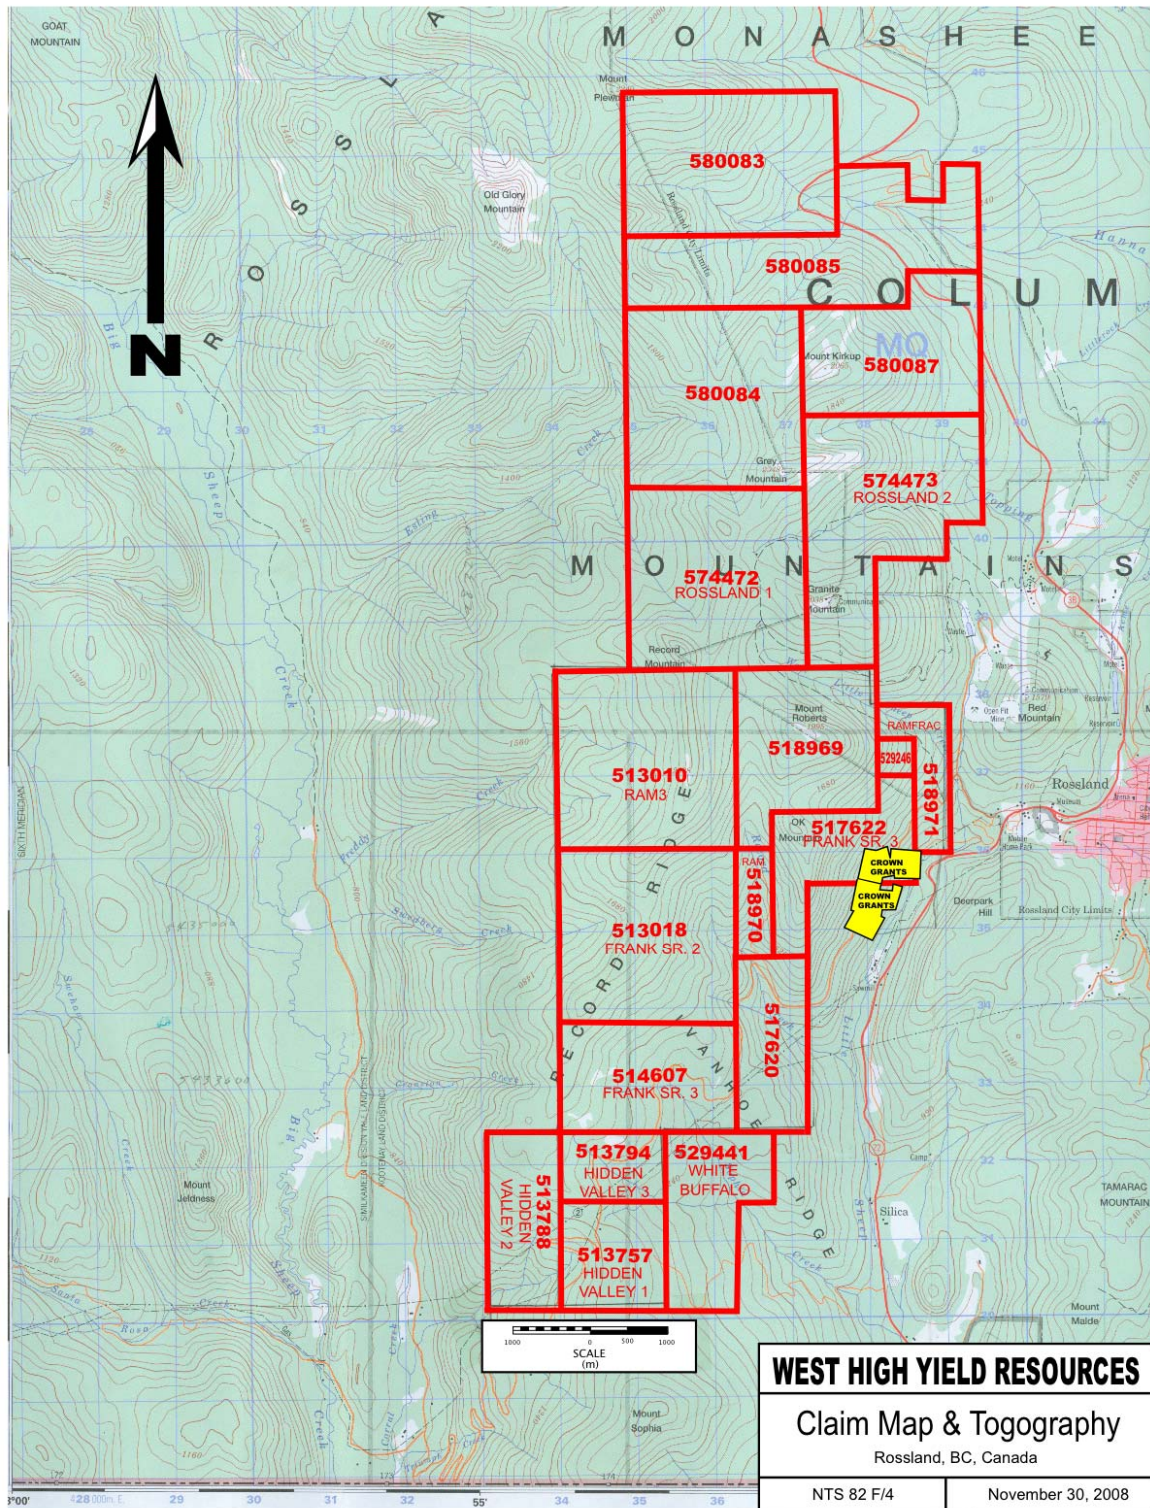


Figure 3 Claim Map & Topography

4. ACCESSIBILITY, CLIMATE, LOCAL RESOURCES INFRASTRUCTURE & PHYIOGRAPHY

4.1 Access

The Record Ridge South property, 11 km southwest of Rossland, is readily reached via the old Cascade Highway (all weather gravel road in fair condition) from Rossland. The Cascade Highway (about 26 km of distance) is maintained throughout the winter.

The town of Rossland is reached via paved highways from Christina Lake, Grand Forks, Castlegar, Trail and Patterson Border Crossing. The closest airport with regularly scheduled service is available at Castlegar, 22 km northeast of Rossland. Rossland can be reached from Vancouver by vehicle on paved Highway #3 with driving time of about 7 hours.

4.2 Climate

The climate in the Rossland area is influenced by British Columbia interior mountainous dry belt with low summer precipitation and cool to cold winters with heavy snowfalls. The annual snowfall averages 370 cm. There is snow a month longer than other region. Average summer temperatures are 25° C and average high 3° C.

The fresh snow in the area occurs by early November and is snow free by the middle of May . Rossland receives about 2000 hours (bright) of sunshine per year without severe windy days. Due to a low summer precipitation in the region, all creeks in the property (specifically in the areas of Ivanhoe Ridge, Record Ridge and Hidden Valley) are dried out after July, necessitating water trucking for water supply in diamond drilling.

4.3 Local Resources and Infrastructure

The proximity of paved Highway #3 and the population (and the potential personnel) centre of Trail (2008 population was 7,237) 5 km east of Rossland and well maintained graveled Cascade Highway and ample nearby hydroelectric sources characterize the property's infrastructure as excellent. Trail, being reached in 10 minutes by driving from Rossland, offers all normal services and supplies including a hospital and adequate accommodations and food establishments to support mining and exploration programs. Basic services such as accommodation, food and fuel are also available in the town of Rossland (population 3,652).

4.4 Physiography (See figure 3)

The property is situated in gently rolling mountainous, wooded terrain of the southeast facing slopes of Record Ridge within the Rossland Range of the Monashee Mountains, a subdivision of the

Columbia Mountain Range. Elevations within the report area vary between 900 and 1700 meters. The three prominent topographic features are 1). Ivanhoe Ridge (peak 1,325 m) in the northern sector, 2). Southeast trending ridge with alpine grass fields between the two main forks of Sophia Creek (named 'Record Ridge South' for this report – northern peak 1,649 m) in the central sector and 3). South trending ridge (peak 1,556 m) south of Hidden Valley in the southern sector. The forgoing all three ridges are gently rolling except the northeastern and western margins where a general slope angle exceeds 30 degrees. The bedrock exposures are relatively abundant (10 to 20 %) in the forgoing all three ridges. Also, the exposures along the Cascade Highway are remarkably noted. It is reported that most of the property area has been once logged and/or burned, but is now again wooded by high standing scrubby spruce, poplar, cedar and balsam. The Sophia Creek and two other creeks on the property are too small to be potentially useful and become dried out in summer. Overburden is thin (1 to 5 meters) or non-existent in the northern and western sectors of the property. The areas above the Cascade Highway, on the eastern slopes, are dominated by glacial till and unsorted gravel exceeding 20 meters.

5. HISTORY

5.1 General History of the Rossland District

The history of the Rossland mining camp dates back to 1890, when the discovery of gold/copper ore in the Red Mountain by Joe Moris and Joe Bourgeois kindled the claim staking rush in Rossland and adjacent Trail area. Subsequently the Rossland mining camp became the second largest lode gold producer in the western Canada. Between 1894 and 1957 the camp produced in excess of 73,860 kilograms of gold, 107,000 kilograms of silver and 54,295 tonnes of copper (Fyles 1984).

West High Yield Resources' four main crown-granted claims (O.K., I.X.L, Midnight and Golden Drip) are situated 2 kilometers northeast of Frank Sr 3 claim for this report. Between 1899 and 1974, 10,492 tonnes averaging 101 grams per tonne gold and 14 grams per tonne silver were produced from these crown granted claims. (Fyles, 1984).

5.2 History of the Record Ridge South Property

In contrast to the extensive work elsewhere in the Rossland district, exploration in the Record Ridge South property has been comparatively limited. There are several old pits and trenches on the property, but there is no good record of conspicuous work ever having been done in the claims prior to 1973.

Based on Minfile (082FSW264), two chromite showings have been prospected, one located on Crown-grants at about 1,341 metres elevation on Ivanhoe Ridge, and the other, about 1.6 kilometers

to the south, at about 1,250 metres elevation on the ridge between the two main forks of Sophia Creek and about 300 metres southeast of the natural gas pipeline (Vandot, 082FSW130).

In 1901, two Crown-granted claims were established on the property and one of them (Burlington lot 4359) was Crown-granted to Bob Lamont.

In 1918, the reverted Crown-grants were leased and additional claims staked by A. Cameron, J. H. MacDonald and Associates. Work was apparently confined to trenching and stripping.

In 1966, the Vandot group of 5-recorded claims was located in the Cascade Highway by V. M. Van of Rossland who deepened the old trenches and sampled.

In 1973, the property was open for claim staking and the “Job” claims were located and jointly owned by George G. Addie and Mineral Resources International Ltd. of Calgary, Alberta. During the period from April 10 to 24, 1973, a magnetometer survey was conducted using the main road (Cascade Highway) and power line as survey control. The survey delineated conspicuous magnetic high anomalies associated with the underlying ultramafic rocks. In 1974, the chromite showings were sampled and analyzed for platinum. 6 samples showed 1.0 to 1.4 grams per tonne platinum, trace silver, trace gold, 0.16 to 0.23 % nickel, 0.18 to 16.5 % chromium and 0.006 to 0.016 % cobalt (Assessment Report 4927).

In 1978, the forgoing “Job” claims were replaced by the “Morrison-White” property containing MAR 1-4, LAND 1-6, SKIN 1-4, ROSS and CAL claims, which were recorded and owned by L. Morrison and A. White. During the period June – October 1978, the 460-hectare grid area was geologically mapped at a scale of 1:2,500, preceded by mapping at a scale of 1: 10,000 on an enlarged aerial photo base. The same area was also surveyed by soil sampling on a 100 metre x 50 metre grid and by magnetic profiling at 10 metre station intervals. In 1979, Lee G. Morrison documented Assessment Report (7162) for United Canso Oil and Gas Ltd., Calgary, Alberta.

In 1984, Noranda Exploration Company held the property as the ROSS 2-3, and CAL claims. Noranda conducted magnetometer surveys over 16 kilometers, induced polarization and electromagnetic surveys over 1 kilometer, a geochemical soil survey comprising 177 samples and trenching.

In 2005, a major portion of the Record Ridge ultramafic body has been staked in part by West High Yield Resources Ltd., Calgary, Alberta.

In May, 2007, West High Yield Resources acquired three mineral claims (Hidden Valley, Hidden Valley 2 and Hidden Valley 3) adjoining to the south of Frank Sr 3 claim. Consequently, West High Yield Resources now owns sufficient mineral claims to cover the entire ultramafic body from the

southern tip of Record Ridge, south to the foot of Mount Sophia and east to Ivanhoe Ridge, an area of 6.2 square kilometers. In 2007, the ultramafic body on the Ivanhoe Ridge, about 1.5 kilometers northeast of the 2008 drill program for this assessment report was tested by line-grid geological mapping, sampling, diamond drilling, and metallurgical testing to assess the economic potential of magnesium-rich nickeliferous cobalt-chromite bearing serpentinite. The total expenditure for the 2007 exploration program was \$1,622,192.

Also, in the entire field season of 2008, the central portion of the Record Ridge ultramafic body (1.5 kilometers southwest of the 2007 exploration program location) was tested by line-grid geological mapping, sampling, diamond drilling, and metallurgical testing to assess the economic potential of magnesium-rich nickeliferous cobalt-chromite bearing serpentinite. The total expenditure for the 2008 exploration program was \$1,562,626.

6. GEOLOGICAL SETTING

6.1 Regional Setting

Adapted from GSC bulletin 108, Andrew, Ash, Hancock, Little, Höy, and Fyles.

In general physiographical and geological view, the Rossland area lies entirely within the Columbia Mountains forming a great triangular, highly mountainous area extending from the International Border to the bend of the Fraser River near Prince George, and being bounded on the east by the Rocky Mountain Trench, and on the west by the Interior Plateau. Rossland area is underlain by rocks that range in age from pre-Pennsylvanian (340 Ma) to Eocene (37-54 Ma), and surficial deposits of Pleistocene (1.5-2 Ma) and Recent age.

Ultramafic rocks in Rossland area, which are the main concern of economic interest for this report, lie approximately 200 kilometers east of the Tulameen-Shulaps belt of ultramafic intrusions (**Fig. 4**), a part of Cordilleran ultramafic intrusions, which are typical of an ophiolites originally composed mainly of olivine and orthopyroxene (harzburgite) and/or clinopyroxene dunite. They characteristically occur as elongate bodies, commonly faulted, sheared and serpentinized. Record Ridge ultramafic rocks of ophiolitic affinity are considered correlative with the Permian Kaslo Group (250-300 Ma) or preferably “Kaslo Assemblage”, and part of the oceanic Slide Mountain Terrain (**Figure 5**).

The late Paleozoic **Mount Robert Formation**, considered coeval with or earlier than the Record Ridge ultramafics, is the oldest rock unit in the report area and exposed west and north of the Rossland district. The Mount Roberts Formation consists of metamorphosed, lower greenschist to amphibolite grade siliceous clastic rocks including grey to black siltstone, argillite and greywacke with lesser carbonaceous and volcanic rocks (Little 1982 and Ash 2003).

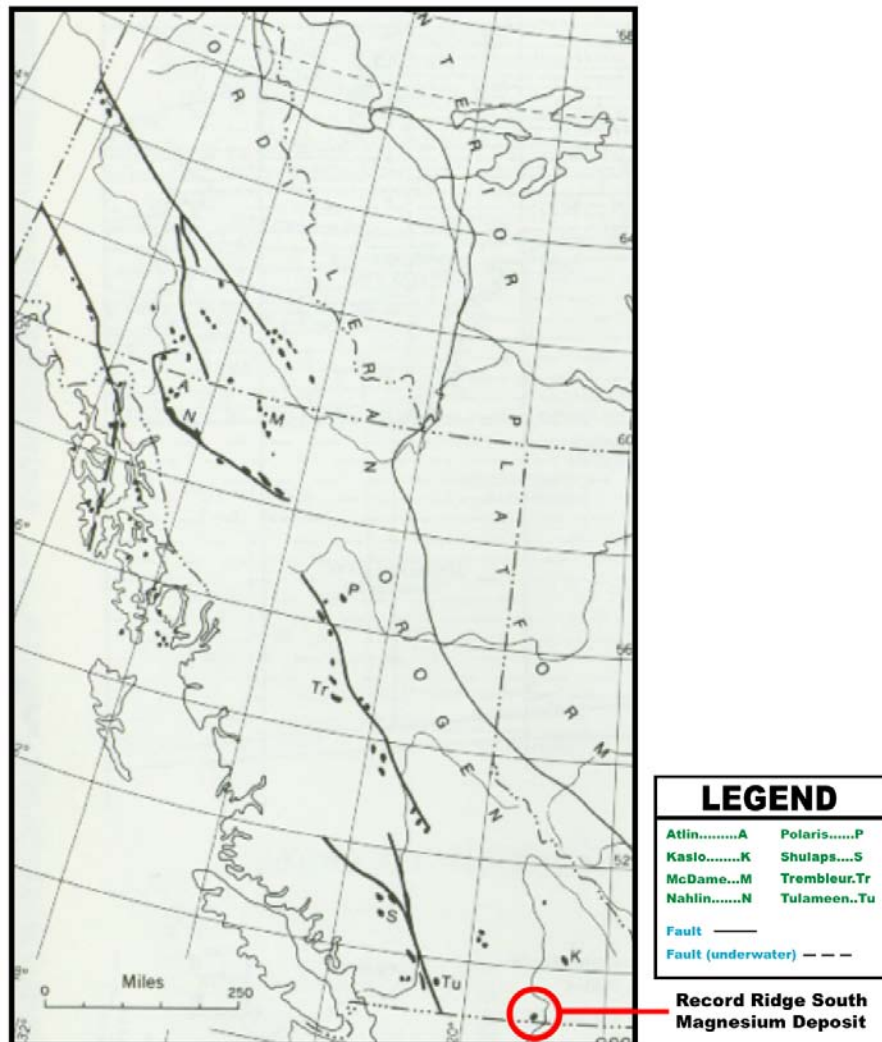



FIGURE 4 – DISTRIBUTION OF ULTRAMAFIC INTRUSION IN THE CORDILLERAN OROGEN, BC, YUKON TERRITORY, & SOUTHEAST ALASKA

(Adapted from: Belyea, H.R., Douglas, R.J.W., Gabrielle, H., Stott, D.F., & Wheeler, J.W. (1968), *Geology of Western Canada*, p.422)

The Early Jurassic (Sinemurian) **Rossland Group** including **Elise Formation** (188-197 Ma) is dominated by mafic and intermediate volcanic and volcanoclastic rocks locally interbedded with marine sediments. Hypabyssal, sub-volcanic intrusions that occur as massive andesite and basalt and augite porphyritic sills and dykes are also a component part of the Rossland Group and primary host for the richest (localized) Cu-Au sulphide veins in the Rossland Gold Camp (Ash 2003). Locally, the Elise formation is overlain by coarse conglomerate of the Upper Cretaceous Sophie Mountain Formation. Both the Early Jurassic Rossland Group and late Paleozoic Mount Roberts Formation are

affected by two major episodes of post-collisional magmatism in the Rossland area. The earliest post-collisional intrusions are represented by the Middle Jurassic Nelson intrusions occurring as batholiths, plutons, stocks and dikes. They range in composition from granodiorite, which is dominant, to quartz diorite, diorite and monzonite (Little 1982). The Middle Eocene Coryell Intrusions and related Marron volcanics (Little, 1982; Ghosh, 1995) are the latest magmatic episodes recorded in the vicinity of the Rossland mining camp. The Coryell intrusions comprise dykes and sills of alkaline syenite that are related to the large Coryell batholith occupying an area of more than 200 square kilometers to the west and north of Rossland.

FIGURE 5– REGIONAL GEOLOGY OF THE ROSSLAND AREA

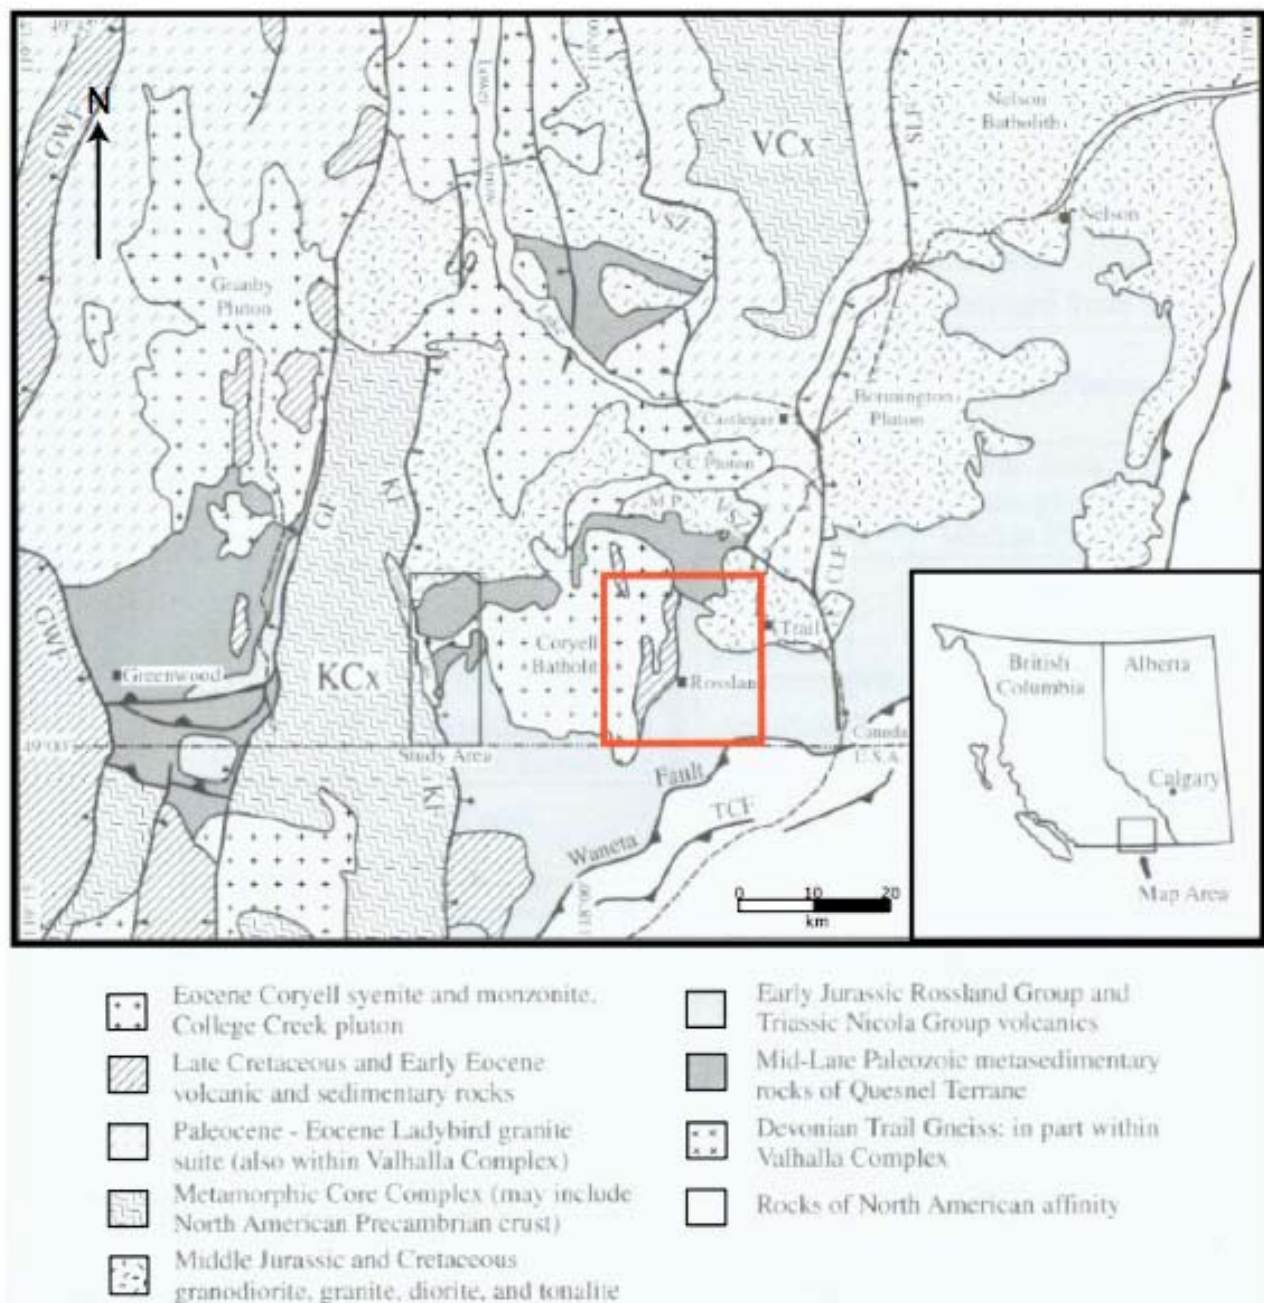


6.2 Regional Structure

The structural framework of the Rossland district is complex, including both compressional and tensional faults, and other tectonic trends including the “Rossland break” which is an east-trending zone of crustal weakness marked by faults and intrusions that include the Rossland monzonite. This major structural break has been confirmed by Hoy and Dunne (2001), who subdivide structural history into three major episodes:

- Extensional tectonism during the deposition of the Elise Formation in Early Jurassic time.
- Compressive tectonism produced east-directed thrust faulting and associated minor folding between 187 and 167 Ma, prior to intrusion Middle and Late Jurassic plutons.
- Normal faulting in the Eocene occurred before and after emplacement of the Coryell intrusions. These faults are numerous, steeply-dipping, north-trending, gouge-gilled structures.

The generalized regional structural cross-section is illustrated on **Figure 6**

FIGURE 6 – REGIONAL CROSS SECTION

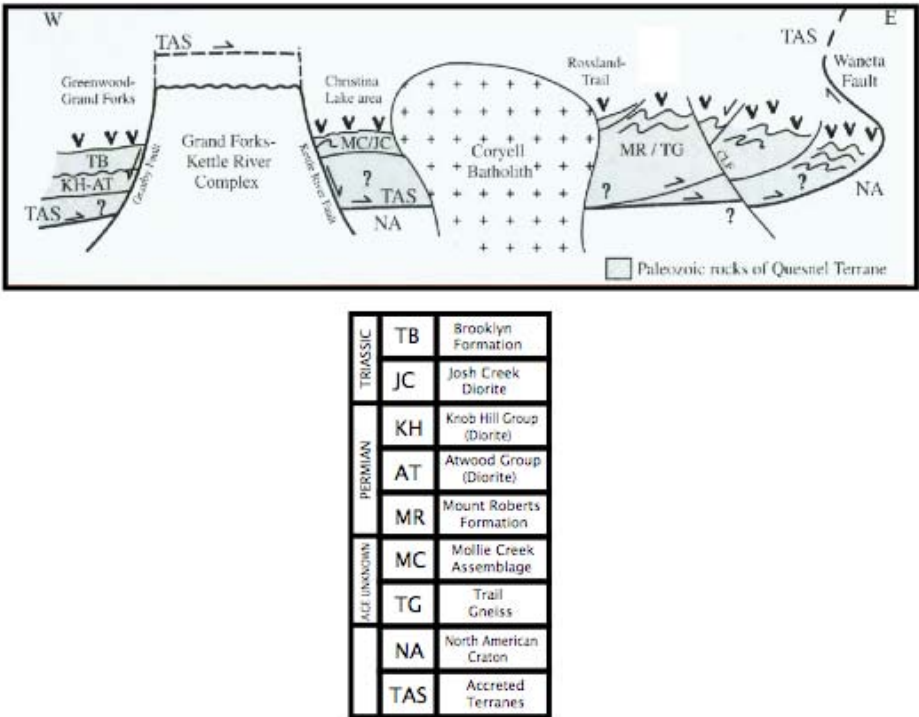

7. LOCAL GEOLOGY

7.1 Occurrences of Ultramafic Rocks in Rossland Area

Illustrated on **Figures 7A**, the Record Ridge ultramafic body magnesium deposit underlies an area of approximately 6.2 square kilometers, 11 kilometers southwest of the town of Rossland (Open File 1990-27) or “Record Ridge ultramafic Body” (BCGS Bulletin 108). The vast area of the western and northern slopes of the Record Ridge Mountain is typified by Coryell intrusions comprising primarily syenite, quartz monzonite and some granite and pulaskite.

The smaller OK ultramafic body, about 1 square kilometer in area occurs in West High Yield Resources’ Crown-granted claims (OK, IXL and Midnight), about 6 kilometers northeast of the 2008 drill program site. As described earlier, OK ultramafic body hosts the rich gold-silver veins averaging 101 grams per tonne gold and 14 grams per tonne silver, but there are no known lode-gold prospects associated with the Ivanhoe Ridge ultramafic body; however it provides more extensive exposure and variation in rock types.

There are also two small ultramafic bodies southwest of the Record Ridge South magnesium deposit; one being in the vicinity of the Velvet mine and the other farther south, on the western slope of Mount Sophia. In bulk view, the Record Ridge ultramafic body and two small bodies lie between a large body of quartz- feldspar porphyry (Little’s map unit **Kqp**) of the late Jurassic on **Fig. 7A** and/or Cretaceous and Coryell intrusions of Eocene age, and probably represent pendants of the larger serpentinite stock.

The Record Ridge ultramafic body comprises variably serpentinized and locally carbonatized ultramafic cumulates. Rock types include dunite, pyroxene-bearing dunite, olivine-bearing wehrlite and lehzolite, each type varying simply as function of the relative proportion of olivine to pyroxene.

Due to pervasive serpentinization, primary mineralogy and textures of the original rocks are almost lost in the area of the eastern part of the ultramafic body. However, the western part of the ultramafic body exposed on the south tip of Record Ridge appears to be less serpentinized or not serpentinized at all, based on Ash (2003), BCGS Bulletin 108 which includes the occurrence of olivine-wehrlite and pyroxene-bearing dunite without notable serpentinization. .

FIGURE 7A—GEOLOGICAL SETTING OF RECORD RIDGE SOUTH MAGNESIUM DEPOSIT

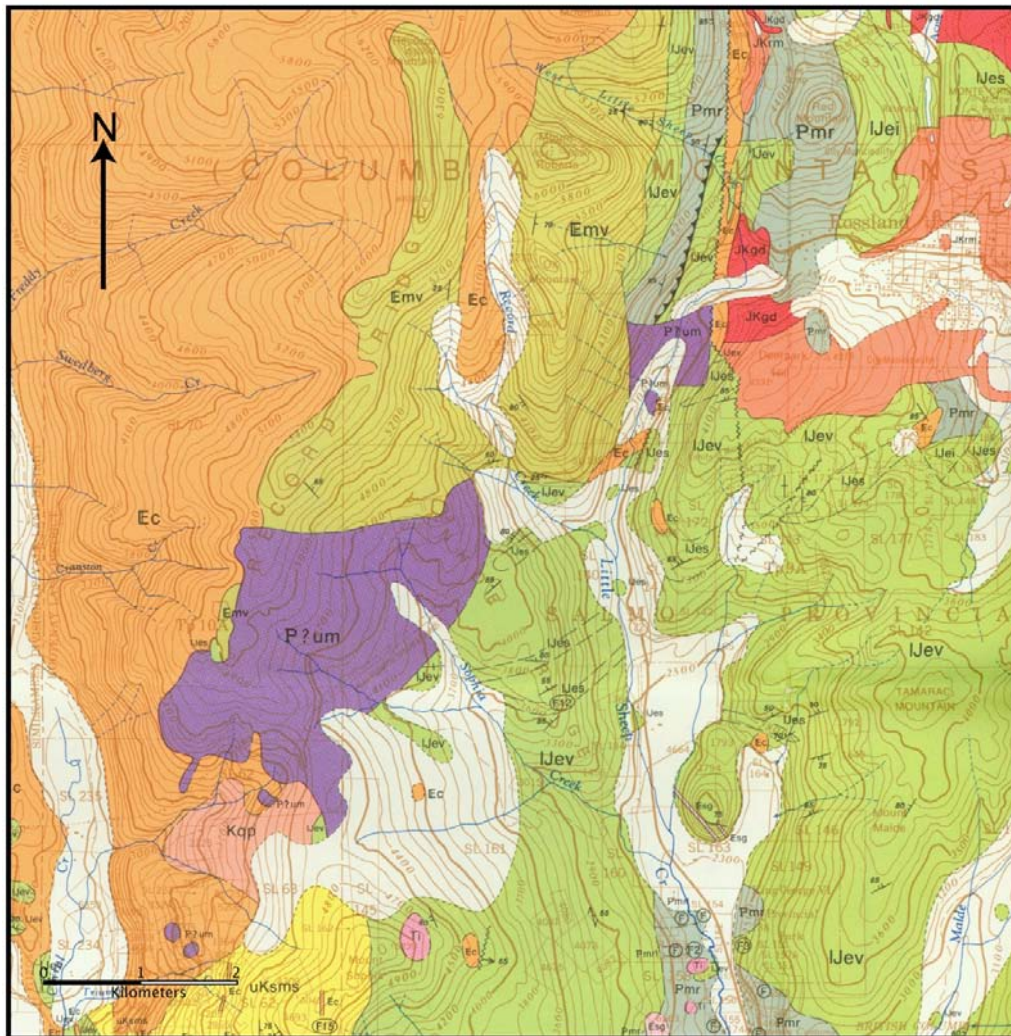


FIGURE 7 B – LEGEND FOR FIGURE 6A



Little (1982) states that the ultramafic bodies were injected into rocks ranging in age from Pennsylvanian (?) to Upper Cretaceous and the larger bodies of serpentinite do not appear to be related to faults except that in Little Sheep Creek where Fyles (1978) mapped the eastern contact as a fault. Although contacts of the ultramafic body were not identified in outcrop, an intrusive relationship was indicated from the actual core logging of six diamond drill holes drilled near the fault contact. Therefore, along the western and southern margins, it is considered that the ultramafic rocks are intruded by Eocene Coryell, sub-volcanic, plutonic rocks and sub-volcanic rocks of the Marron Formation. However, the inferred northern contact of the body is marked by a linear topographic depression, which Fyles (1984) interpreted as a faulted contact. A minor increase of alteration intensity in the ultramafic rocks towards the contact suggests that the fault has been

affected by only limited movement or is restricted to late, high level brittle faulting. The results of core logging of seven diamond drill holes drilled in 2007 near the northern contact substantiate Fyles' interpretation of the northern faulted contact.

Along its eastern margin the body is reported to be in contact with massive fine-grained, aphanitic mafic volcanic rocks correlated with the Rossland Group by Little (1982) and Höy, and Andrew (1991a). Ash (2003) considered this contact is indicated to be a faulted contact, due to the presence of fish-scaled serpentine with localized carbonate-altered shear zones near the margin of the ultramafic body. It is noted that the actual drill cores from 4 holes drilled near a part of the eastern contact consist of medium/coarse-grained diorite to gabbro in an intrusive contact with serpentinite.

Suggestions as to the origin of the ultramafic rocks in the Rossland camp have varied. Early workers (Brock, 1906; Drysdale, 1915) interpreted them to be altered augite porphyrite stocks. Little (1982) was the first to suggest that they are most likely contemporaneous with the Paleozoic, oceanic Mount Roberts Formation, and part of an ophiolitic assemblage. Fyles (1984) interpreted the ultramafic rocks to be much younger, possibly of Late Cretaceous age, inferring that they are post-collisional intrusions. Höy, and Andrew (1991 b) recognized that the ultramafic rocks are most probably tectonically emplaced.

7.2 Lithology of the Record Ridge Ultramafic Body

7.2.1. Ultramafic Rocks (See Figure 8)

As described in the preceding section, the ultramafic rocks in the eastern part of the Record Ridge ultramafic body for the most part are dominated by moderate to intensely serpentinized dunite, and peridotite (wehrlite or lehrzoite) except the localized unaltered ultrabasic rocks in places. In the field, all serpentinized ultramafic rocks are simply named as "serpentinite". The most abundant variety of serpentinite is a dense, black, massive and highly magnetic with rare disseminated chromite. Another type of serpentinite is greenish black or milky white to grey colored with a variegated/veined appearance (pale creamy green alternating with dark-green, principally due to significant secondary magnetite along veins and hairline fractures) with minor sulfides and chromite. Near the south margins of the body in the vicinity of Hidden Valley, the serpentinite on surface and from drill cores is often highly altered with pronounced development of yellow and green steatite ($\text{Mg}_3\text{Si}_4\text{O}_{10}(\text{OH})_2$) and talc-carbonaceous blebs in stockworks of thin veins or mottled appearance.

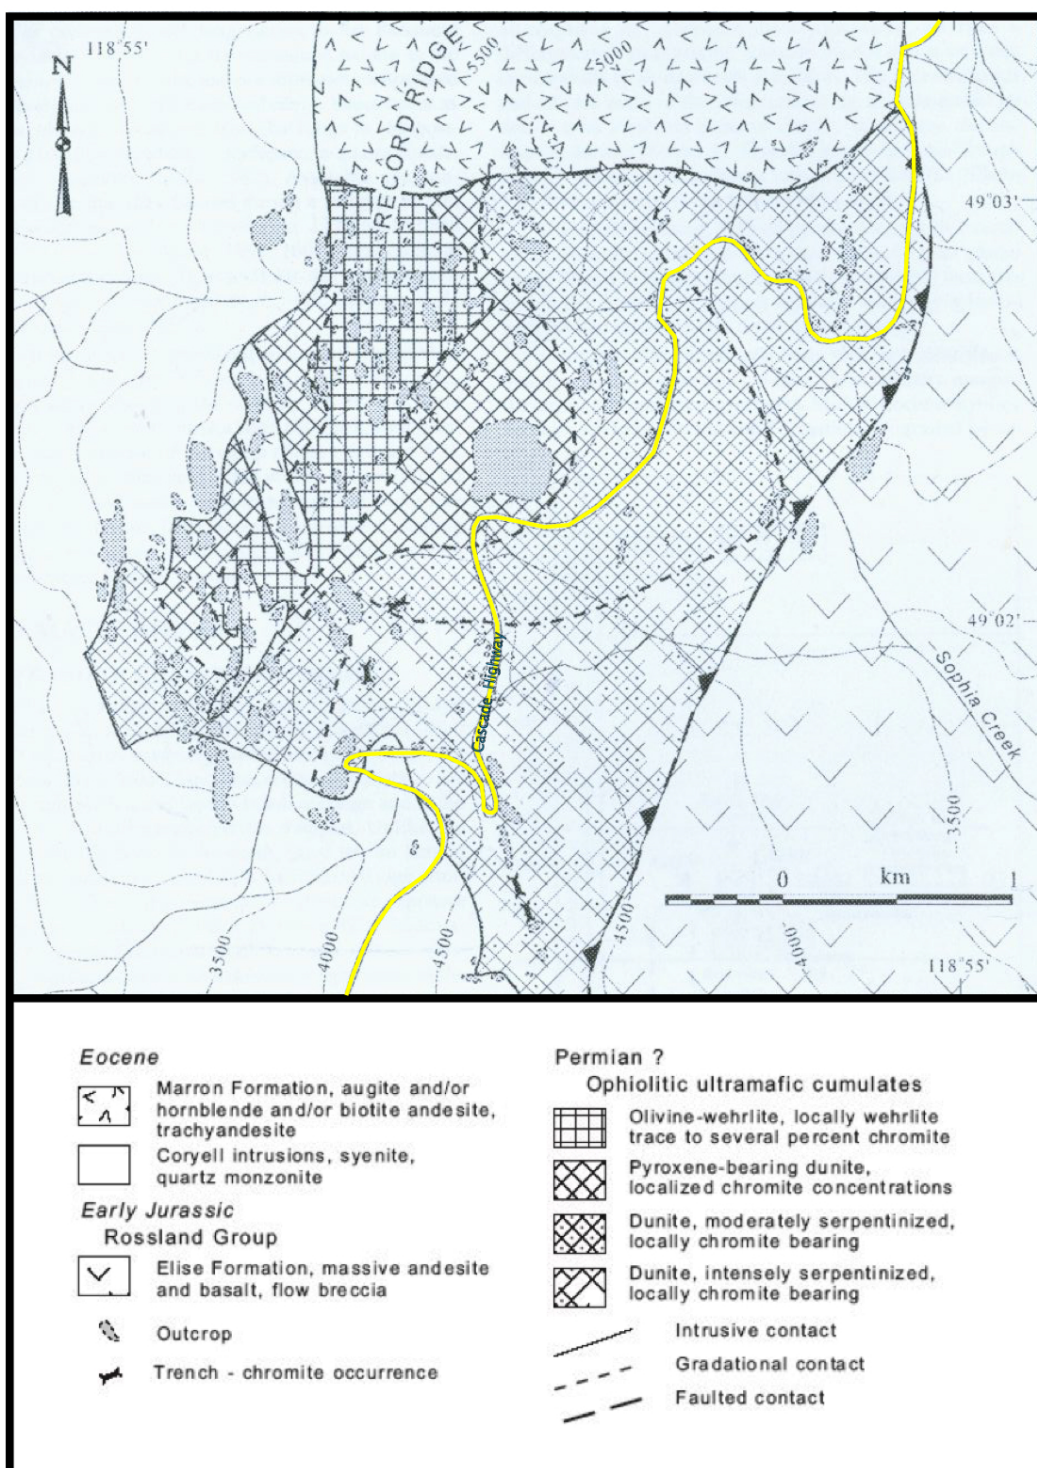


FIG. 8 LOCAL GEOLOGY OF THE RECORD RIDGE ULTRAMAFIC BODY

As noted earlier, the ultramafic rocks in the western part of the Record Ridge body are mapped to be olivine-wehrlite, locally wehrlite pyroxene-bearing dunite without notable serpentinization (BCGS Bulletin 108).

Petrographic study of the ultramafic rocks provides a reasonable evidence in support of an ophiolitic affinity and pervasive serpentinization together with talc-sericite and carbonate (magnesite/calcite) alteration in the initial ophiolites. Based on petrographic study of 27 thin sections from specimens collected in 2007 and 2008, a modal mineralogy in polished thin sections of the ultramafic rocks in the Record Ridge ultramafic body is summarized in the following table :

Modal Mineralogy in Thin Sections of the Ultramafics in the Record Ridge South Ultramafic Body
After Craig Leitch, Ph.D (2007 and 2008)

Olivine %	Serpentine %	Amphibole Secondary Tremolite & Actinolite %	Talc/ Sericite %	Magnetite %	Carbonate/ Magnesite/ Calcite %	Chromite %	Pentlandite Pyrrhotite Pyrite %
25 - 90	15 -90	1 - 20	2 - 35	2- 5	1 – 5	1 – 5	Trace – 1

7.2.2. Thickness of Ultramafic Rocks

Continuous with the 2007 diamond drilling, the completed 2008 definition drill program had also intersected broad zones of rich magnesium bearing ultramafic rock (serpentinized dunite, weherlite and lehzolite). The southern sector of the resource definition drilling tested by 28 holes gave a wide zone of serpentinite from surface to an average of 75 metres except at or near, the contact with the volcanics and intrusives to the southwest. The northern sector, tested by 21 holes shows a broader zones of serpentinite from surface to an average of 105 metres, which is open to the west. (**Figure 9**).

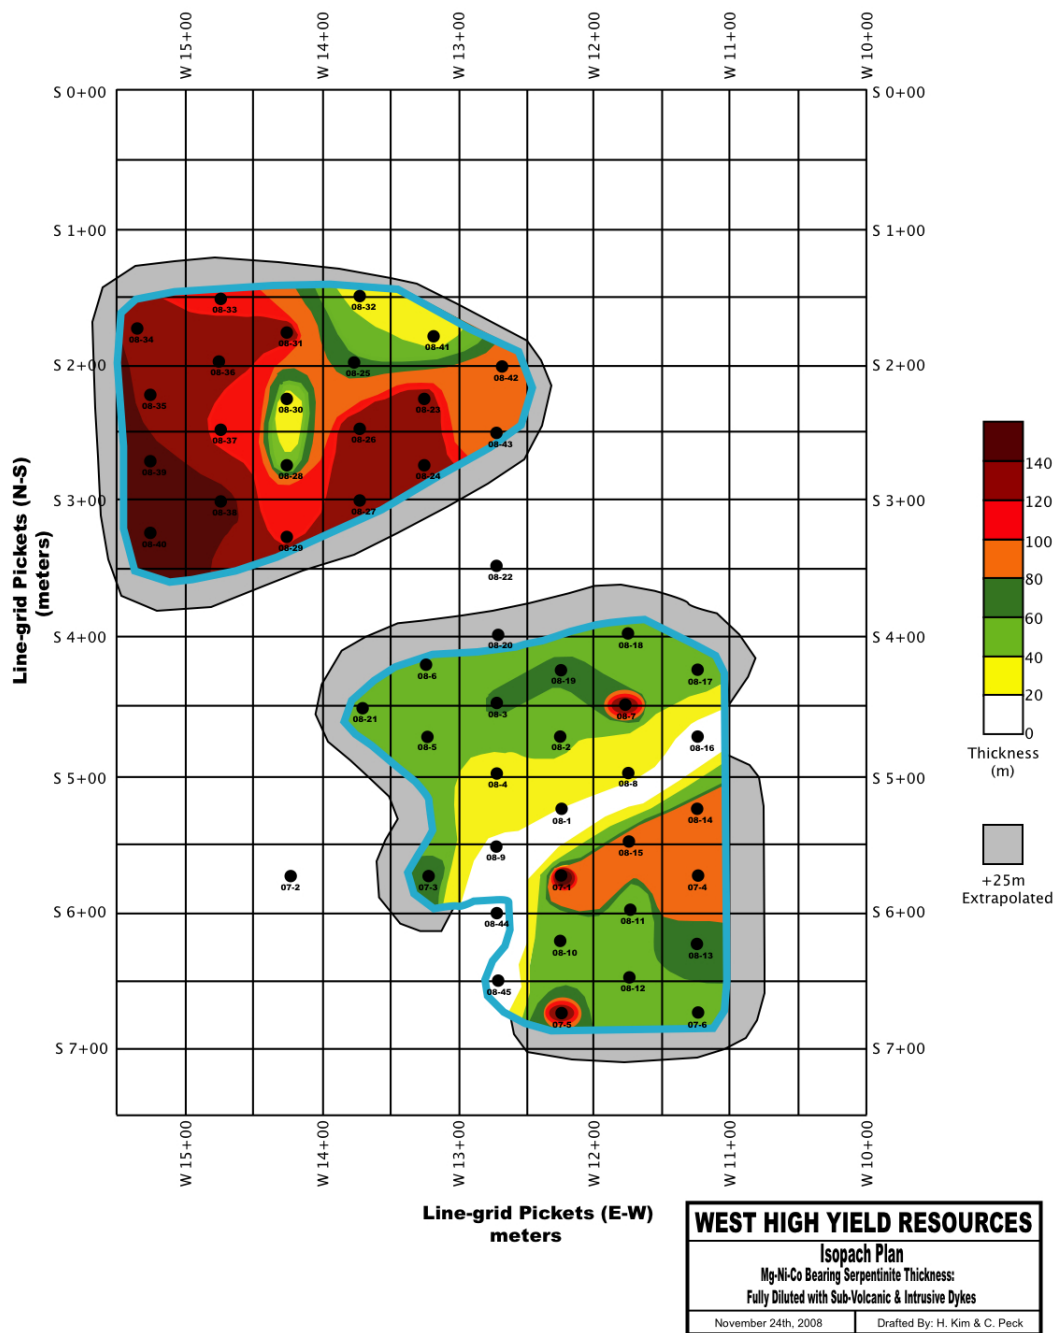


Figure 9 Isopach Plan – Serpentine Thickness from Surface

7.2.3. Volcanic, Sub-volcanic and Intrusive rocks

The boundaries of the Record Ridge ultramafic body are fault or shear zones with Tertiary Coryell intrusions and Marron volcanic flows with hypabyssal intrusions (37-54 Ma) and early Jurassic Elise Formation volcanic flows (172-195 Ma). Consequently, many intrusive rocks as dikes or sill-like apophyses related to the Elise lavas or Coryell intrusions are conspicuously noted in the serpentinite, ranging in drill length of volcanic and intrusive rocks from 1 m to 70 m. The dykes and sills of the volcanic to sub-volcanic and intrusive rocks into the serpentinites on the surface are generally outlined in the 2008 drill line grid area (**Figure 10**).





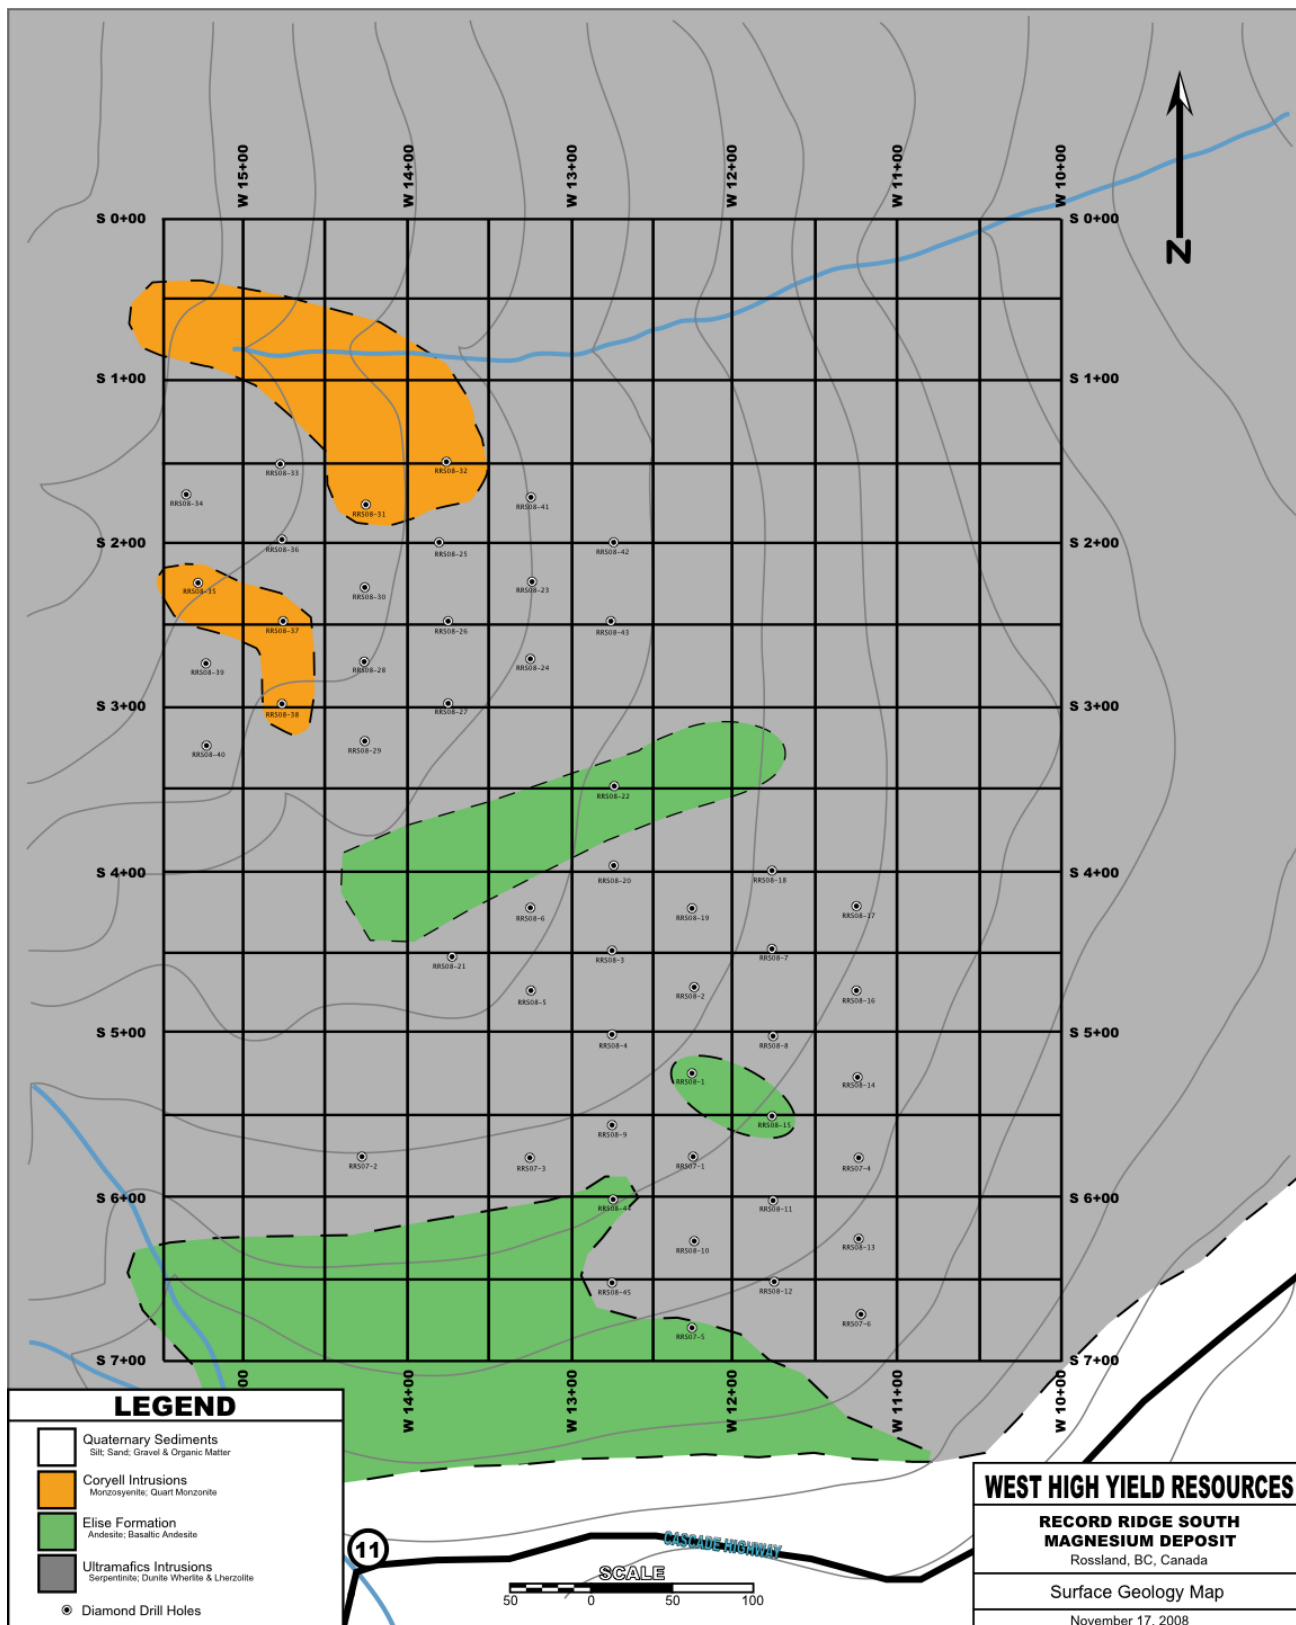


Figure 10 - 2008 Drill Program Line Grid Geology

The rocks intervened in the serpentinite include massive andesite, basalt, basaltic andesite, trachyandesite, trachyte, diorite, gabbro, monzo-gabbro, lamprophyre, syenite, monzonite, monzodiorite, augite porphyry and biotite latite porphyry. For a simple demonstration of geology profile of the Record Ridge South Magnesium Deposit, all intervened volcanic and intrusive rocks are grouped to one unit as waste rock and shown in green color on the geological cross sections (Figures 11, 12, 13 and 14).

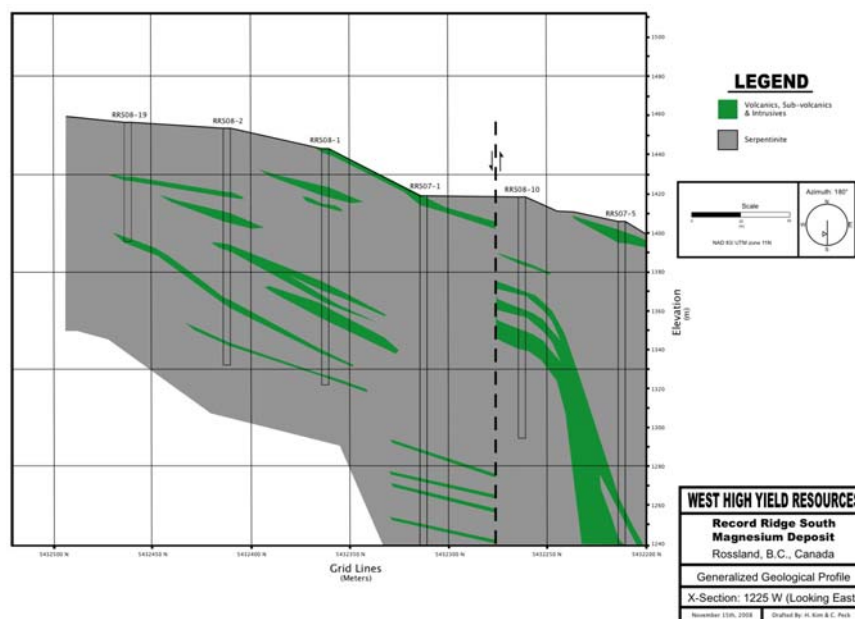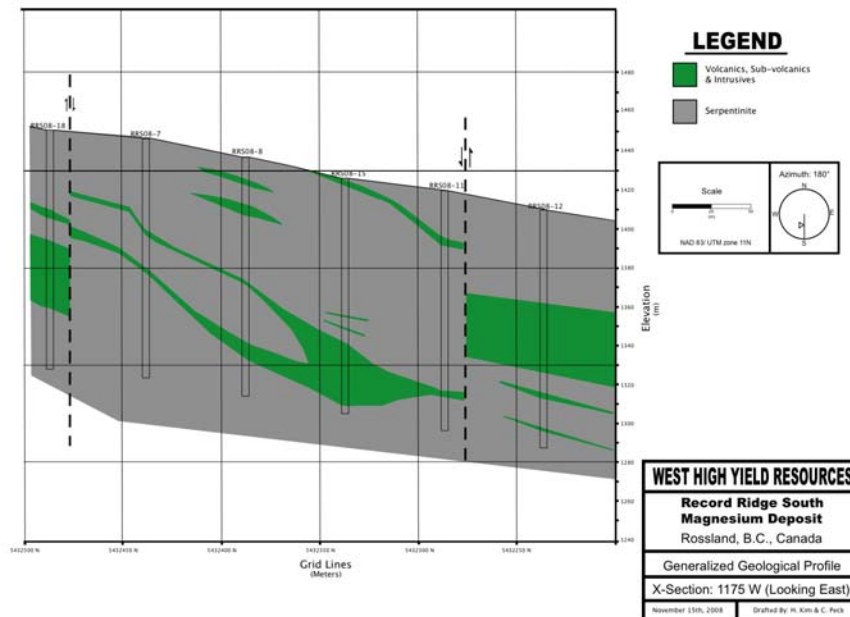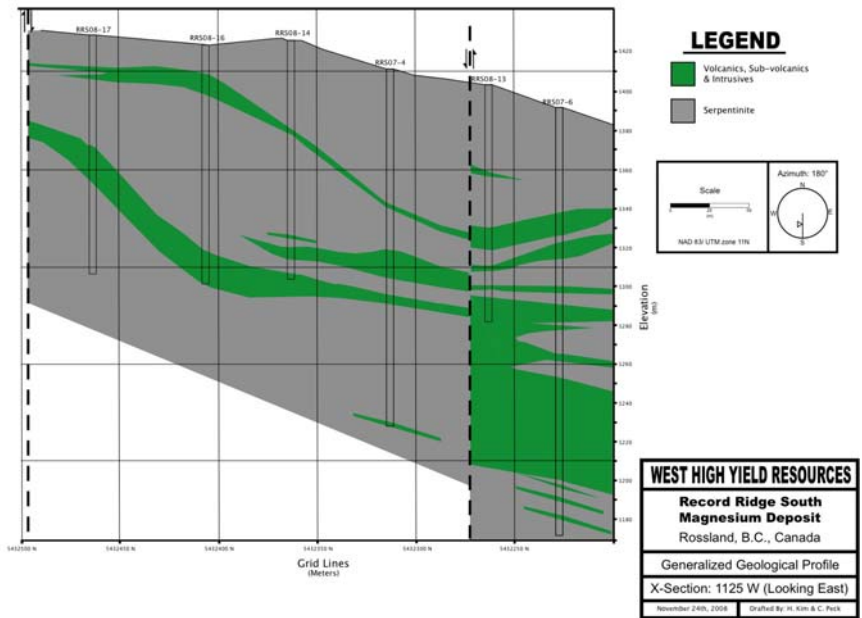

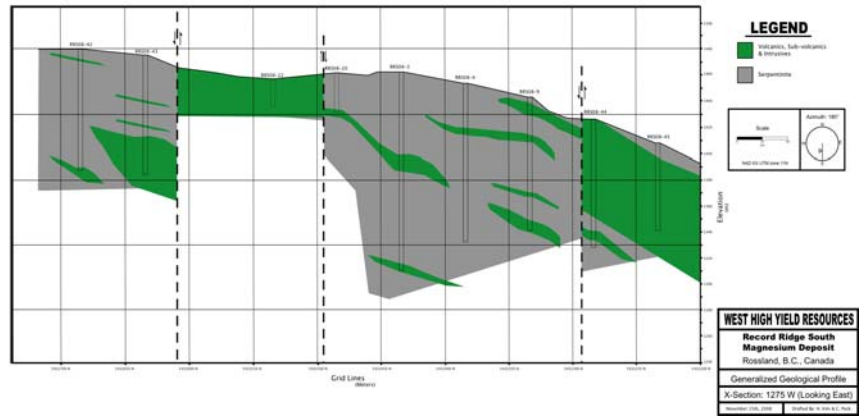

8. MINERALIZATION

8.1 Magnesium and Nickel

The results of combined 2007 and 2008 diamond drilling programs indicate that the Record Ridge ultramafics host a significant magnesium and nickel mineralization of economic interest. The strong demand for magnesium - growth is around 4 % to 6 % per annum - is driven by the metal's unique properties that so far have no substitutes. Magnesium is as strong as steel and 40% lighter than aluminium. It readily alloys, and is easy to machine and cast. The current market price of magnesium is U.S \$2.30 per pound or US \$5071per mt (January 11, 2009: source from "Magnesium.com. U.S. Spot Dealer").

Whole rock ICP-AES (four-acid "Near-Total" digestion) has shown consistent high magnesium and anomalous nickel values throughout the ultramafic body.

The following table summarizes the drill intersections of the serpentinite with contained magnesium and nickel values, which are fully diluted with intervened volcanic, sub-volcanic and intrusive rocks with contained lower magnesium and nickel values:

TABLE 1
Summary of Serpentinite Intersections**(diluted with sub-volcanic and intrusive dykes)**
2007 & 2008 Definition Drilling Program for Measured Mineral Resource Estimation
Record Ridge South Magnesium-Nickel Exploration Project
Rossland, BC

1. All holes drilled in vertical
2. Length shown in green with “122.2” represents serpentinites from surface
3. Blank columns represents “Assay in progress”.

DDH #	Depth (meters)		Length (meters)	Magnesium %	Nickel %	Remark
	From	To				
RRS08-1	0.0	19.6	19.6	21.9	0.22	
	25.9	68.9	43.0	22.9	0.21	Incl. one dyke(1.9 m)
	89.1	122.8	33.7	24.5	0.21	Incl. 2 dykes (0.7 m & 1.1 m) totaling 1.8 m
RRS08-2	0.0	44.0	44.0	24.0	0.22	Incl. one dyke(3.3 m)
	50.3	123.4	73.1	23.9	0.21	Incl.3 dykes (1.1 & 3.6 m thick) totaling 5.9 m
RRS08-3	1.8	63.0	61.2	25.0	0.22	Incl. one dyke(0.85 m)
	79.4	149.7	70.3	23.9	0.20	Overlain (intrusive and /or in fault) by basaltic andesite to diagabbro(16.4 m)
RRS08-4	1.8	36.0	34.2	25.8	0.23	
	40.9	123.1	82.2	26.9	0.24	Incl. one dyke(1.85 m)
RRS08-5	0.6	45.3	44.7	24.0	0.21	Incl. one dyke 2 m thick
RRS08-6	1.2	54.8	53.6	24.0	0.22	
RRS08-7	1.2	123.4	122.2	24.4	0.23	Incl. two dykes; 1.4 m & 2.05 m thick
RRS08-8	1.5	25.2	23.7	21.0	0.18	Incl.one dyke(3.2 m thick)
	31.4	96.3	64.9	24.5	0.27	Incl. one dyke (0.4m)
	104.6	123.7	19.1	25.5	0.19	Incl. one dyke (0.6 m)
RRS08-9	16.9	29.4	12.5	20.9	0.19	Capped by the diagabbro (andesite) mixed with serpentinite
	35.9	73.6	37.7	21.6	0.19	
	77.6	94.5	16.9	18.5	0.16	
RRS08-10	0.6	59.4	58.8	19.7	0.17	Incl. two dykes; 0.7 m & 2. 7 m thick, totaling 3.4 m
	64.7	71.7	7.0	17.0	0.15	
	80.9	126.8	45.9	24.0	0.21	
RRS08-11	1.2	25.4	24.2	23.6	0.20	
	29.7	123.8	94.1	25.3	0.21	Incl. one dyke (0.83m)
RRS08-12	1.2	49.0	47.8	26.4	0.22	
	82.7	122.2	39.5	26.7	0.22	Incl. 2 dykes (1.7 & 2.6 m thick) totaling 4.3 m Overlain by diagabbro (33.7 m thick)
RRS08-13	1.2	75.1	73.9	25.7	0.20	Incl. one dyke 2 m thick
RRS08-14	0.6	98.2	97.6	25.1	0.20	Incl. one dyke 1.55 m thick
RRS08-15	0.6	84.1	83.5	22.7	0.20	Incl. 3 dykes (07– 1.6 m thick) totaling 3.6 m
	0.7	13.7	13.0	19.8	0.19	The eastern fringe

RRS08-16	27.0	106.0	79.0	21.8	0.20	Overlain (intrusive and /or in fault) by basaltic andesite to diagabbro(13.3 m)
RRS08-17	1.2	58.1	56.9	21.5	0.20	Incl. 2 dykes (1.4 & 2.9 m thick) totaling 4.3 m
	77.1	123.4	46.3	26.4	0.19	Overlain (intrusive and /or in fault) by basaltic andesite to diagabbro(19 m)
RRS08-18	0.6	67.2	66.6	22.5	0.20	Near the northern fringe
RRS08-19	0.0	60.8	60.8	22.4	0.20	Incl. one dyke 2 m thick; near the northern fringe;
RRS08-20	0.0	27.5	27.5	18.6	0.17	At the northern fringe; Shut down in fault zone
RRS08-21	0.0	58.9	58.9	22.5	0.20	At the western fringe; incl. one dyke 3 m thick
RRS08-22						No serpentinite intersection
RRS08-23	28.6	152.4	123.8	23.7	0.21	Incl. one dyke (0.7 m) within the Monzo-syenite dyke sill zone; capped by monzo-syenite; 20.7 m
RRS08-24	2.7	135.3	132.6	24.3	0.24	Incl. one dyke (0.9 m)
RRS08-25	0.6	11.6	11.0	22.5	0.20	Within the monzo-syenite dyk -sill zone
	27.7	88.4	60.7	23.9	0.22	Overlain (intrusive and /or in fault) by basaltic andesite to diagabbro(16.1m)
	104.5	123.8	19.3	25.4	0.23	Overlain (intrusive) by basaltic andesite to diagabbro(16.1m)
RRS08-26	1.2	123.8	122.6	22.7	0.20	Incl. 2 dykes (1.2 & 2.5 m thick) totaling 3.7 m
RRS08-27	1.0	123.8	122.8	24.1	0.21	Incl. 2 dykes , 2 m & 2.3m thick totaling 4.3 m
RRS08-28	0.0	41.4	41.4	24.3	0.22	
RRS08-29	0.0	117.9	117.9	21.7	0.19	Incl. 3 dyke , 1.3 – 2.5 m totaling 5.7 m
RRS08-30	0.0	40.0	40.0	22.9	0.22	Near the monzo-syenite dyke- sill zone
	47.8	124.6	76.8	25.1	0.23	Overlain (intrusive) by monzo-gabbro 7.8 m
RRS08-31	31.9	154.5	122.6	27.7	0.20	Capped by monzo-syenite within the monzosyenite dyke sill zone
RRS08-32	0.0	36.5	36.5	23.9	0.22	Incl. one dyke 2.4 m
	53.3	114.8	61.5	22.5	0.21	Incl. one dyke (1.9 m); overlain by 16.8 m of basaltic andesite to diagabbro;
RRS08-33	0.0	117.3	117.3	25.6	0.22	
RRS08-34	7.7	143.0	135.3	24.5	0.20	Incl. 2 dykes (0.8 & 1.9 m thick) totaling 2.7 m
RRS08-35	1.0	123.7	122.7	26.7	0.24	Incl. 4 dykes (0.97 – 2.2 m thick) totaling 6.5 m
RRS08-36	0.0	124.4	124.4	24.3	0.19	
RRS08-37	14.9	123.7	108.8	24.6	0.20	Capped by monzo-syenite
RRS08-38	8.4	154.2	145.8	26.8	0.20	Incl. one dyke (0.85 m); capped by monzosyenite(7 m)
RRS08-39	0.9	154.5	153.6	26.6	0.20	Incl. one dyke (0.6 m)
RRS08-40	0.2	148.4	148.2	25.3	0.20	Incl. 3 dykes (0.3 – 3.5 m thick) totaling 5 m
RRS08-41	0.0	19.9	19.9	26.6	0.20	
	49.3	83.7	34.4	26.0	0.21	Overlain (intruded and/or in fault)by monzo-syenite (29.3 m)
RRS08-42	0.2	89.5	89.3	24.2	0.20	Incl. one dyke (1.5 m)
RRS08-43	1.5	63.6	62.1	25.1	0.20	Incl. two dykes (1.7 & 2 m thick) totaling 3.7 m
RRS08-44	75.2	86.0	10.8	20.0	0.16	Capped by the volcanics in the southwestern fringed
RRS08-45	5.8	18.0	12.2	16.9	0.17	Near the contact with the volcanics in the southwestern fringe

RRS07-1	14.2	204.6	190.4	21.3	0.19	Incl. 5 dykes (1.08 – 2.26 m thick) totaling 7.56 m
RRS07-2	2.0	19.8	17.8	25.6	0.22	Near the contact with the volcanics;
RRS07-3	9.5	73.0	63.5	22.6	0.19	Western fringe near the contact with the volcanics ; incl. one dyke 3 m thick
RRS07-4	2.2	94.5	92.3	25.0	0.21	Incl. one dyke (0.85 m)
	109.9	118.4	8.5	31.3	0.20	Overlain (intrusive) by diagabbro(15.4 m)
	123.4	182.8	59.4	25.5	0.22	Overlain (intrusive) by diagabbro (5 m)
RRS07-5	3.5	170.2	166.7	25.2	0.20	Incl. one dyke (1.5 m)
	197.6	210.1	12.5	19.9	0.14	
RRS07-6	3.9	59.0	55.1	25.0	0.20	Southeastern fringe
	83.6	96.0	12.4	29.1	0.23	
	99.9	105.7	5.8	28.9	0.23	
	118.2	130.5	12.3	24.4	0.19	
	134.8	142.7	7.9	24.8	0.20	

The nickel values in the above chart include nickel in both sulphide and non-sulphide minerals as “total nickel”. In 2008, a total of 21 drill cores samples were tested for nickel sulphide by Assayers Canada and Acme Lab., both in Vancouver, BC. Assayer Canada gave nickel sulphide values from a low of 0.09 % NiS to a high of 0.16 % NiS. Acme Lab’s assay report shows also the same range of nickel sulphide values that Assayers Canada reported.

8.2 Cobalt

Based on the analytical data for 61 holes drilled in 2007 and 2008, the cobalt values contained in the serpentinite of the Record Ridge ultramafic body are running from 77 g/t (77 ppm) to 126 g/t (126 ppm) averaging 106 g/t Co.

8.3 Chromium

In 2008, only selected samples were tested for chromium values. The following chart summarizes the chromium values for the selected 13 holes drilled in 2007 and 2008:

Summary of chromium values in serpentinite

. Length shown in green with “61.2” represents serpentinites from surface without major sub-intrusive dykes

DDH #	Depth (meters)		Length (meters)	Cr %	Remark
	From	To			
RRS08-1	0.00	19.6	19.6	0.51	
	25.9	68.9	43.0	0.30	Incl. one dyke(1.9 m)

	89.1	122.8	33.7	0.26	Incl. two dykes; 0.7 m & 1.1m
RRS08-2	0	33.1	33.1	0.30	
	36.4	44.0	7.6	0.28	
	50.3	60.9	10.5	0.38	
	64.6	90.2	25.7	0.35	
	92.5	123.4	30.9	0.25	Incl. one dyke(1.1 m)
RRS08-4	1.8	36.0	34.4	0.30	
	40.9	123.1	82.2	0.53	Incl. one dyke(1.85 m)
RRS08-5	0.6	22.3	21.7	0.35	
	24.3	45.3	21.0	0.34	
RRS08-6	1.2	54.8	53.6	0.34	
RRS08-7	1.2	123.4	122.2	0.36	Incl.2 dykes(1.4 m & 2.05 m thick)
RRS08-8	1.5	12.5	11.0	0.31	
	15.7	25.2	9.5	0.37	
RRS07-1	14.2	179.4	165.2	0.29	Incl.4dykes(1.08 – 1.68 m) totaling 5.3 m
	181.7	204.6	22.9	0.23	
	237.9	254.5	16.6	0.19	Incl. one dyke (0.89m)
RRS07-2	2.0	19.8	17.8	0.29	Near the contact with the volcanics
RRS07-3	9.5	73.0	63.5	0.27	Western fringe near the contact with the volcanics ; incl. one dyke 3 m thick
RRS07-4	2.2	94.5	92.3	0.35	Incl. one dyke (0.85 m)
	109.9	118.4	8.5	0.41	Overlain (intrusive) by diagabbro(15.4 m)
	123.4	182.8	59.4	0.31	Overlain (intrusive) by diagabbro (5 m)
RRS07-5	3.5	170.2	166.7	0.33	Incl. one dyke (1.5 m)
	197.6	210.1	12.5	0.22	
RRS07-6	3.9	59.0	55.1	0.27	Southeastern fringe
	83.6	96.0	12.4	0.27	
	99.9	105.7	5.8	0.26	
	118.2	130.5	12.3	0.33	
	134.8	142.7	7.9	0.31	
Average				0.33	Weighted average

8.4 Base Metal and Precious Metal Occurrences

8.4.1. Base metal showings

The base metal occurrences on the Record Ridge property reported by Lee Morrison (1979) could not be recovered in 2007 and 2008. Morrison (1979) states that “there is a group of pits and trenches near on old cabin on the east side of the Record Ridge at line grid 5S, 9W.” In 2007,

Morrison's 1979 line grids were totally disappeared and it was not able to relocate the old cabin, pits and trenches. " Five grab samples of weathered material from the shears (10 cm wide and 10 m long) contained traces of gold and from 12 to 80 grams of silver/tonne. Three samples assayed for base metals contained an average of 0.8% Cu, 0.4% Pb and 0.4% Zn, although no lead or zinc-bearing minerals were identifiable." (Morrison 1979).

The strongly kaolinized and manganese stained shear zone in the old adit "consisted of visually only crystalline pyrite, but a sample from the shear zone contained 0.6 % Pb, 0.3% Cu and 0.7% Zn (Morrison 1979).

8.4.2. Chromite Showings

Three chromite showings were reported by Morrison (1979). "The best of three is at 31S, 8W where there is a vertical lens of massive chromite up to 30 cm wide in a nearly vertical sheared zone striking N30°W. The walls also contain disseminated chromite within a patchy band up to 10 m wide". " Two selected grab samples of massive chromite from several large trenches (at about 7W between 39S and 42S) averaged 29.8% Cr₂O₃, 17.2% Fe₂O₃ and 0.08% TiO₂."(Morrison 1979).

8.4.3. Precious Metal Showings

Based on the results of 2007 and 2008 drilling, the Record Ridge ultramafics erratically contain quartz veins with sulphide mineralization (mainly pyrite) and are disseminated by pyrite or pyrrhotite throughout the property. On the actual drill core logging and assaying, no precious metal mineralization is recognized. The best drill core sample from the Record Ridge property is 0.24 g/t Au over 1.5 m from hole RRS07-1. The assay results of other selected 80 samples returned a negative value, 0.001 – 0.007 g/t Au. Three grab samples of sulphides (mainly pyrite) taken by Morrison (at line 22S between 18W and 19W) contained "only trace of gold and 3 grams silver/tonne." "Within the wedge of Rossland formation west of 15W baseline between 18S and 27S, where several old pits in rusty sediments and andesite are located, selected samples returned only trace of gold and an average of 8 grams silver per tonne."(Morrison 1979).

8.5 Platinum Group Elements

The assay results of 5 surface and 70 drill selected core sample from the Record Ridge ultramafic rocks in 2007 returned a negative value for platinum and palladium, not exceeding <0.01 g/t. However, it should be noted, " a probable selected sampling of serpentinite for platinum returned an assay of 1.02 grams per tonne (Addie, 1973). Subsequent work by other companies has failed to

reproduce the platinum results (Open File 1900-27.

9. EXPLORATION

Unlike most of the properties near Rossland, BC, the Record Ridge South properties have had very little exploration done on them. There appears to be some old abandoned pits and trenches, however, the first documented exploration in this area was in 1973.

In 1973, Mineral Resources International Ltd., Calgary, AB, owned the “Job” claims, located on Ivanhoe Ridge. George G. Addie, who was a P.Eng. & P.Geo., was retained by this company to conduct a magnetometer survey in April, 1973. The survey was done using the Cascade Highway and adjacent power lines as controls. The survey found anomalous zones within the property that were linked to the occurrence of magnetite within the ultramafic serpentinite body that lies within the Ivanhoe Ridge area.

In 1974, the same company had six chromite-bearing ultramafic rocks sampled and noted the following values:

- Platinum: 1.0-1.4 g/t
- Silver: Trace
- Gold: Trace
- Nickel: 0.16-0.23%
- Cobalt: 0.006-0.016%
- Chromium: 0.18-16.5%

(Assessment Report 4927)

The next documented work on the property occurred in 1978, when the claims MAR 1-4, LAND 1-6, SKIN 1-4, ROSS and CAL, became the “Morrison-White” property. The property was evaluated on behalf of United Canso Oil and Gas, Calgary, AB.

The 460-hectare grid area was geologically mapped at a scale of 1: 2,500, preceded by mapping at a scale of 1: 10,000 on an enlarged aerial photo base. The same area was also surveyed by soil sampling on a 100 meter x 50 meter grid and by magnetic profiling at 10 meter station intervals.

Their work concluded that eight of the eleven soil geochemical anomalies located on the property are of sufficient interest to warrant further geophysical and/or geochemical evaluation (Assessment Report 7162).

The next documented exploratory work was in 1984, by Noranda Exploration Company, who held the

CAL and ROSS 2-3 claims. The company performed trenching, soil sampling, which consisted of 177 separate samples, a magnetometer survey over 16 km, as well as induced polarization and EM surveys over 1 km.

Finally, in 2007 and 2008, West High Yield Resources, Calgary, AB, conducted a 51 hole diamond drill program as well as surface mapping and surface sampling, with the hopes of determining the economic potential of the magnesium-rich nickeliferous cobalt-chromium bearing ultramafic rocks that underlie the property.

10. DRILLING

10.1 Introduction

The 2008 drill program consisted of 45 NQ holes totaling 5,279 meters. All of the holes were drilled vertically. The holes were laid 50-meters apart on square grid, according to a line grid that was established by Hango Land Surveyors, Castlegar, BC. The holes ranged in depths from a minimum of 30.2 meters (RRS08-20) to a maximum of 154.5 meters (RRS08-39).

Dip tests were conducted at approximately 61-meter intervals, using REFLEX EZ-SHOTTM drill hole equipment. All hole UTM coordinates collar elevations and grid locations in metres are summarized in the following table:

2008 Diamond Drill Hole Particulars

Hole Number	UTM Northing	UTM Easting	Elevation (m)	Line west	Line south	Depth drilled	Remark
RRS08-1	5432364	434677	1445.2	1225	525	122.8	
RRS08-2	5432414	434677	1456.2	1225	475	123.4	
RRS08-3	5432439	434627	1465.6	1275	450	153.9	
RRS08-4	5432389	434627	1456.7	1275	500	123.1	
RRS08-5	5432414	434577	1470.5	1325	475	74.7	
RRS08-6	5432464	434577	1473.6	1325	425	93.3	
RRS08-7	5432439	434727	1446.7	1175	450	123.4	
RRS08-8	5432389	434727	1437.6	1175	500	123.7	
RRS08-9	5432339	434627	1445.6	1275	550	103.9	
RRS08-10	5432264	434677	1420.6	1225	625	126.8	
RRS08-11	5432289	434727	1420.3	1175	600	123.7	
RRS08-12	5432239	434727	1410.5	1175	650	122.2	

RRS08-13	5432264	434777	1405.1	1125	625	122.8	
RRS08-14	5432364	434777	1427.3	1125	525	123.7	
RRS08-15	5432339	434727	1426.8	1175	550	120.7	
RRS08-16	5432407	434779	1425.2	1123	482	123.7	
RRS08-17	5432464	434777	1430.4	1125	425	123.4	
RRS08-18	5432489	434727	1447.8	1175	400	122.2	
RRS08-19	5432464	434677	1458.6	1225	425	63.5	
RRS08-20	5432489	434627	1463.4	1275	400	30.2	
RRS08-21	5432439	434527	1476.1	1375	450	116.7	
RRS08-22	5432539	434627	1463.5	1275	350	29.3	
RRS08-23	5432664	434577	1491.7	1325	225	152.4	
RRS08-24	5432614	434527	1498.2	1375	275	154.2	
RRS08-25	5432686	434520	1506	1382	203	123.8	
RRS08-26	5432639	434527	1503.8	1375	250	123.8	
RRS08-27	5432589	434527	1496.1	1375	300	123.8	
RRS08-28	5432614	434477	1514.3	1425	275	75	
RRS08-29	5432561	434477	1500	1425	328	123.7	
RRS08-30	5432667	434477	1514.7	1425	222	124.6	
RRS08-31	5432714	434477	1518.7	1425	175	154.5	
RRS08-32	5432740	434537	1504.5	1365	149	114.8	
RRS08-33a	5432736	434427	1531.4	1475	153	17	Fault zone (no drill log)
RRS08-33b	5432736	434427	1531.4	1475	153	117.3	
RRS08-34a	5432701	434361	1547	1541	188	14.6	Fault zone (no drill log)
RRS08-34b	5432701	434361	1547	1541	188	143	
RRS08-35	5432661	434373	1543.3	1529	228	123.7	
RRS08-36	5432693	434422	1533.4	1480	196	124.4	
RRS08-37a	5432640	434431	1525.2	1471	249	39	Fault zone (no drill log)
RRS08-37	5432640	434431	1525.2	1471	249	123.7	
RRS08-38	5432589	434427	1514.7	1475	300	154.2	
RRS08-39	5432614	434377	1530.9	1525	275	154.5	
RRS08-40	5432564	434374	1517.3	1528	325	148.4	
RRS08-41	5432714	434577	1492.8	1325	175	88.1	
RRS08-42	5432689	434627	1482.5	1275	200	93.5	
RRS08-43	5432639	434627	1479.4	1275	250	93.3	
RRS08-44	5432289	434627	1427.7	1275	600	109.4	
RRS08-45	5432239	434627	1414.9	1275	650	72.9	

10.2 Drill Results

Based on core logging and available analytical data, highlight of the intersected magnesium-nickel-cobalt-chromite bearing serpentinites from the 2007 and 2008 drill programs are summarized in the following charts:

TABLE 2
Summary of Serpentine Intersections without major intervened dykes
Record Ridge South Magnesium-Nickel Exploration Project,
Rosland, BC

▪ Length shown in green with “ 132.6 ” represents serpentinites from surface without major sub-intrusive dykes

▪ .N.A = not assayed

DDH #	Depth (meters)		Length (meters)	Ni %	Co g/t	Mg %	Cr %	Remark
	From	To						
RRS08-1	0.00	19.6	19.6	0.22	100	21.9	0.51	
	25.9	68.9	43.0	0.20	100	22.9	0.30	Incl. one dyke(1.9 m)
	89.1	122.8	33.7	0.21	105	24.5	0.26	Incl. two dykes; 0.7 m & 1.1m
RRS08-2	0	33.1	33.1	0.23	94	25.5	0.30	
	36.4	44.0	7.6	0.23	89	24.5	0.28	
	50.3	60.9	10.5	0.21	95	24.9	0.38	
	64.6	90.2	25.7	0.24	114	25.7	0.35	
	92.5	123.4	30.9	0.22	104	25.0	0.25	Incl. one dyke(1.1 m)
RRS08-3	1.8	63.0	61.2	0.22	106	25.0	N/A	Incl. One dykes(0.85m)
	79.4	109.0	29.6	0.22	108	25.0	N/A	Incl. one dyke(0.8 m)
	111.5	149.7	38.2	0.21	101	24.0	N/A	
RRS08-4	1.8	36.0	34.4	0.23	109	26.4	0.30	
	40.9	123.1	82.2	0.24	95	26.9	0.53	Incl. one dyke(1.85 m)
RRS08-5	0.6	22.3	21.7	0.24	99	26.4	0.35	
	24.3	45.3	21.0	0.20	97	23.0	0.34	
RRS08-6	1.2	54.8	53.6	0.22	108	25.6	0.34	
RRS08-7	1.2	123.4	122.2	0.23	100	25.3	0.36	Incl.2 dykes(1.4 m & 2.05 m thick)
RRS08-8	1.5	12.5	11.0	0.19	89	24.0	0.31	
	15.7	25.2	9.5	0.20	97	25.3	0.37	
	31.4	96.3	64.9	0.20	100	23.8	0.28	Incl. one dyke(0.4 m)
	104.6	123.7	19.1	0.19	88	25.5	0.31	Incl. one dyke(0.6m)
RRS08-9	16.9	29.4	12.5	0.19	83	20.9	0.63	Capped by mainly diagabbro mixed with serpentinite
	35.9	73.6	37.7	0.19	97	21.6	0.23	
	77.6	94.5	16.9	0.16	85	18.5	N/A	

RRS08-10	0.6	33.7	33.1	0.20	98	21.9	N/A	
	36.4	59.4	23.0	0.14	77	18.0	N/A	Incl. one dyke (0.7 m); serpentinite with banded soapstones
	64.7	71.7	7.0	0.15	83	17.0	N/A	Serpentinite with banded soapstones
	80.9	126.8	45.9	0.21	106	24.0	N/A	

RRS08-11	1.2	25.4	24.2	0.20	105	23.6	N/A	
	29.7	123.8	94.1	0.21	115	25.3	N/A	Incl. one dyke (0.83m)
RRS08-12	1.2	49.0	47.8	0.22	103	26.4	N/A	
	82.7	94.7	12.0	0.23	118	28.6	N/A	Overlain(intruded) by diagabbro (33. 7 m)
	97.3	112.5	15.2	0.25	105	29.3	N/A	Overlain by diagabbro (2.6 m)
	114.2	122.2	8.0	0.24	82	27.5	N/A	
RRS08-13	1.2	75.1	73.9	0.20	75	25.7	N/A	
	86.4	110.3	23.9	0.15	68	20.1	N/A	
RRS08-14	0.6	98.2	97.6	0.20	89	25.1	N/A	Incl. one dyke (1.55 m)
RRS08-15	0.6	84.1	83.5	0.20	101	22.7	N/A	
RRS08-16	0.7	13.7	13.0	0.19	90	19.8	N/A	The eastern fringe
	27.0	106.0	79.0	0.20	96	21.8	N/A	Mixed soapstone and serpentinite
RRS08-17	1.2	58.1	56.9	0.20	100	21.5	N/A	
	77.1	123.4	46.3	0.19	100	26.4	N/A	
RRS08-18	0.6	67.2	66.6	0.20	101	22.5	N/A	Near the northern fringe
RRS08-19	0.0	60.8	60.8	0.20	97	22.4	N/A	Incl. one dyke (2 m)
RRS08-20	0.0	27.5	27.5	0.17	90	18.6	N/A	Shut down in the fault zone
RRS08-21	0.0	29.5	29.5	0.20	103	23.2	N/A	
	34.1	58.9	24.8	0.22	113	24.7	N/A	
RRS08-23	28.6	152.4	123.8	0.21	106	23.7	N/A	Within the Monzo-syenite dyke sill zone; capped mainly by monzo-syenite; 20.7 m
RRS08-24	2.7	135.3	132.6	0.24	106	24.3	N/A	Incl. one dyke (0.9 m)
RRS08-25	0.6	11.6	11.0	0.20	100	22.5	N/A	Within the monzosyenite dyke- sill zone
	27.7	88.4	60.7	0.22	105	23.9	N/A	Overlain by 16.1 m diagabbro
	104.5	123.8	19.3	0.23	107	25.4	N/A	Overlain by 16.1 m mozo-syenite
RRS08-26	1.2	105.8	104.6	0.21	104	23.0	N/A	Incl. one dyke (1.2 m)
	108.3	123.8	15.5	0.20	107	23.9	N/A	

RRS08-27	1.0	63.5	62.5	0.20	105	24.4	N/A	
	65.8	70.8	5.0	0.18	102	21.8	N/A	
	72.8	123.8	51.0	0.24	106	25.7	N/A	
RRS08-28	0.0	41.4	41.4	0.22	116	24..3	N/A	
	0.0	26.3	26.3	0.19	96	22.0	N/A	

RRS08-29	28.8	69.4	40.6	0.22	102	22.9	N/A	
	74.5	117.9	43.4	0.21	99	22.8	N/A	
RRS08-30	0.0	40.0	40.0	0.22	108	22.9	N/A	
	47.8	124.6	76.8	0.24	112	25.1	N/A	Chromium > 10% at 116.8 -119.8
RRS08-31	31.9	154.5	122.6	0.20	116	27.7	N/A	Capped by monzo-syenite
RRS08-32	0.0	36.5	36.5	0.22	107	23.9	N/A	
	53.3	91.3	38.0	0.22	100	22.5	N/A	
	93.2	114.8	21.6	0.21	106	23.8	N/A	
RRS08-33	0.0	117.3	117.8	0.22	109	25.6	N/A	
RRS08-34	7.7	124.7	117.0	0.19	107	24.3	N/A	
	126.6	143.0	16.4	0.23	122	28.3	N/A	
RRS08-35	1.0	38.4	37.4	0.26	128	28.9	N/A	
	40.6	111.3	70.7	0.21	115	26.4	N/A	Incl.2 dykes(0.9 m & 1.5 m) totaling 2.4 m
	113.2	123.7	10.5	0.20	125	27.4	N/A	
RRS08-36	0.0	107.8	107.8	0.19	110	24.6	N/A	
	110.2	124.4	14.2	0.22	112	25.7	N/A	
RRS08-37	14.9	123.7	108.8	0.20	112	24.6	N/A	Capped by monzo-syenite
RRS08-38	8.4	154.2	145.8	0.20	118	26.8	N/A	Incl. one dyke (0.85 m); capped by 7 m of monzosyenite
RRS08-39	0.9	154.5	153.6	0.20	116	26.6	N/A	Incl. one dyke (0.6 m)
RRS08-40	0.2	23.1	22.9	0.20	128	27.4	N/A	
	26.6	148.4	121.8	0.20	108	25.5	N/A	Incl. one dyke (1.2 m)
RRS08-41	0.0	19.9	19.9	0.20	113	26.7	N/A	
	49.3	83.7	34.4	0.21	111	26.0	N/A	
RRS08-42	0.2	89.5	89.3	0.20	132	24.2	N/A	Incl. one dyke (1.5 m)
RRS08-43	1.5	54.9	53.4	0.20	107	25.5	N/A	Incl. one dyke (1.7 m)
	56.9	63.6	6.7	0.22	104	26.4	N/A	
RRS08-44	75.2	86.0	10.8	0.16	87	20.0	N/A	capped by the volcanics in the southwestern fringe
RRS08-45	5.8	18.0	12.2	0.17	96	16.9	N/A	Near the contact with the volcanics in the southwestern fringe
RRS07-1	14.2	179.4	165.2	0.20	99	21.7	0.29	Incl.4dykes(1.08 – 1.68 m) totaling 5.3 m
	181.7	204.6	22.9	0.17	100	20.7	0.23	
	237.9	254.5	16.6	0.14	101	17.9	0.19	Incl. one dyke (0.89m)
RRS07-2	2.0	19.8	17.8	0.22	118	25.6	0.29	Near the contact with the volcanics
RRS07-3	9.5	73.0	63.5	0.19	99	22.6	0.27	Western fringe near the contact with the volcanics ; incl. one dyke 3 m thick
RRS07-4	2.2	94.5	92.3	0.21	110	25.0	0.35	Incl. one dyke (0.85 m)
	109.9	118.4	8.5	0.20	108	31.3	0.41	Overlain (intrusive) by diagabbro(15.4 m)
	123.4	182.8	59.4	0.22	115	25.5	0.31	Overlain (intrusive) by diagabbro (5 m)
	3.5	170.2	166.7	0.20	113	25.2	0.33	Incl. one dyke (1.5 m)

RRS07-5	197.6	210.1	12.5	0.14	78	19.9	0.22	
RRS07-6	3.9	59.0	55.1	0.20	105	25.0	0.27	Southeastern fringe
	83.6	96.0	12.4	0.23	118	29.1	0.27	
	99.9	105.7	5.8	0.23	121	28.9	0.26	
	118.2	130.5	12.3	0.19	95	24.4	0.33	
	134.8	142.7	7.9	0.20	111	24.8	0.31	

Note: Hole RRS08-22 was stopped in the intrusive rocks from surface to the depth of 23.8 m without serpentinite

10.3 Geotechnical logging

In 2008, no geotechnical logging was conducted. However, the results of 2007 geotechnical logging can be utilized for understanding the geotechnical rock quality of the 2008 drill cores, as the drill intersected serpentinites in 2007 and 2008 are mutually identical. As reported in the 2007 diamond drill assessment report, all drill cores in 2007 were subjected to a series of geotechnical tests, in order to determine certain qualities of the rock. In 2007, the tests were performed every 1-5 meter, depending on the homogeneity of the rock. The specific gravity of the core samples was measured using a scale and graduated cylinder. Next the rock quality was determined using the Q-system ($Q = (RQD / J_n) * (J_r / J_a) * (J_w / SRF)$), where RQD= Rock quality designation; J_n = Joint set number; J_r = Roughness of the most unfavorable joint or discontinuity; J_a = Degree of alteration or filling along the weakest joint; J_w = Water inflow; SRF= Stress reduction factor

A sample geotechnical log from 2007 drill program was presented in **Appendix II** of the 2007 diamond drill assessment report.

11. SAMPLING METHODS AND ANALYSIS

All of the drill cores were placed into wooden boxes, each containing approximately five meters of NQ core. The boxes were then brought to the Midnight camp, where it is was logged. The logging consisted of detailed analysis of the geology, sample design and geotechnical logging to determine the specific gravity and Q-value of the rock. The Ultramafic serpentinite samples were divided into 1.5-meter sections, while the other rock samples (volcanic and sub-volcanic dykes) were divided into 2-meter samples.

The core was then split by a diamond saw with half of the 1.5-meter rock sample going into a plastic bag containing a unique sample identification number, and the other half of the rock sample being returned to the wooden box from which it came. The boxes of split core were then moved to secure, metal freight containers that are located on site.

The plastic bags containing the core samples were placed into heavy-duty rice sacks and shipped to Assayers Canada Ltd., Vancouver, BC, for chemical analysis. All 3,330 drill core samples were subjected to ICP-AES analysis of 24 elements, atomic absorption for precious metals and fusion analysis. The multi-ICP was chosen to indicate the concentrations of magnesium, nickel, cobalt, chromium and other trace elements, while the fusion tests were done primarily to attain the chromium concentrations.

A 212-kilogram bulk sample was sent to Met-Solve Laboratories Inc. for the purposes of determining the possibility of extracting magnesium and nickel from the serpentinites. The samples for metallurgical testing were prepared by using a diamond saw to quarter selected samples that were stored at the midnight camp

The rock samples that were sent for analysis are currently being stored at Assayers Canada Ltd., Vancouver, BC.

12. DATA VERIFICATION

All drill logs, analysis and assay certificates are contained in the files of West High Yield Resources, and are looked after by a qualified professional.

13. MINERAL PROCESSING AND METALLURGICAL TESTING

Metallurgical testing was conducted by Met-Solve Laboratories Inc. (www.met-solve.com), 8815 Eastlake Drive, Burnaby, BC V5A 4T7. SGS Lakefield Research Ltd. Two metallurgical tests were completed by Met-Solve. Initially, 12 kilograms of drill cores were tested to find a possibility of magnesium recovery by leaching. Subsequently the final metallurgical test program for the 200 kilograms of drill cores was completed by Met-Solve. In the following, Met-Solve Laboratories' two metallurgical tests are briefly summarized:

Results of the Initial Metallurgical Test Program for the Magnesium Recovery.

For the initial preliminary metallurgical testing, 12 kilograms of drill cores from hole RRS07-1 (drilled in 2007) containing an average of 26 % Mg and 0.23 % total Ni were sent to Met-Solve Labs. Met-Solve's report gave the best result of magnesium recovery , **84.5%** of the Mg by sulphuric acid (H₂SO₄) leaching at 70° C to produce magnesium sulphate (MgSO₄) and **77%** of the Mg by hydrochloric acid leaching(HCl) to produce magnesium chloride(MgCl₂).

Results of the Final Metallurgical Test Program for the Magnesium Recovery.

Encouraged by the significant results of magnesium recovery by the preliminary metallurgical testing, 200 kilograms of drill cores for normal metallurgical testing were sent to Met-Solve Laboratories. The normal metallurgical test work consisted primarily of sulphuric acid(H_2SO_4) and hydrochloric acid(HCl) leaching at variable temperatures, up to 70° , preceded by gravity concentration, floatation separation and magnetic separation tests. The drill cores for this normal metallurgical testing were selected from 8 holes in the southern sector of the Record Ridge South containing an average of over 25 % Mg. Using hydrochloric acid leaching method, Met-Solve Labs was able to liberate **78.6 %** magnesium in the form of magnesium chloride (MgCl_2).

Two metallurgical test reports with a detailed explanation of the procedures and results can be found in **Appendix III** of this assessment report.

14. MINERAL RESOURCE AND MINERAL RESERVE ESTIMATES

No estimates of mineral resources or mineral reserves have been made for this report, but it should be noted that a technical report for a NI 43-101 mineral resource estimation of the Record Ridge South Magnesium Deposit is being independently prepared by SRK Consulting Engineers & Scientists (Bart Stryhas, Ph.D), *7175 West Jefferson Avenue Suite 3000 Lakewood, Colorado 80235 USA*.

15. INTERPRETATION AND CONCLUSIONS

Based on the results of 2007 and 2008 diamond drilling, the Record Ridge ultramafic rocks host a significant magnesium mineralization of strong economic interest. Ultramafic rocks are characterized by high magnesium (Mg) weight percent (wt%). In the overall property, magnesium values are averaged to be 24.5 wt % Mg or 46.6 wt % of MgO .

The final metallurgical test report for magnesium recovery by Met-Solve Laboratories Inc. gave an encouraging finding to result in extraction of 78.6 % of the magnesium in the form of magnesium chloride(MgCl_2) into solution by hydrochloric acid leaching method.

The 2008 line-grid drill program for a resource estimation can be divided into two sectors (northern and southern) by an east-west trending fault on line 350S **.(Figs. 2 & 10)**. The southern sector of resource definition drilling tested by 24 holes gave positive values of magnesium (24 % Mg) over widths from surface, ranging from 11 to 122.2 metres and averaging 40 metres.

Contrastingly, the northern sector tested by 21 holes returned high values of magnesium (25.1% Mg) with broad zones of ultramafic rocks from surface or near surface, ranging from 36.5 metres to 148.2 metres and averaging 100 meters. This wide zone of the magnesium rich serpentinite is open to the west.

.The Record Ridge ultramafics contain also other metals of economic interest. The nickel values in the ultramafics are averaging 0.20 % Ni. The cobalt values are running from 77g/t to 126 g/t Co. The chromite values range from 0.25 % to 0.45% Cr averaging 0.33 % Cr..

With a view to the forgoing potential economic interest and an exploration of the magnesium rich ultramafic rocks (olivine wehrlite, wehrlite and pyroxene bearing dunite), continuously from the 2008 drill sites (northern sector of resource estimation), 2009 drilling should be moved progressively westward on a 50-metre square grid pattern to increase further mineral resource in compliance with National Instrument 43-101 and CIM definition.

16. RECOMMENDATIONS

The authors are of the opinion that the Record Ridge South Magnesium Deposit is of sufficient merit to warrant further investigation by drilling and metallurgical testing for extraction of the final magnesium alloy product. A program of detail geological mapping and surface sampling should be performed in the entire western part of the Record Ridge ultramafic body comprising the exposures of olivine wehrlite, wehrlite and pyroxene bearing dunite.

In 2009, NQ drill holes should be laid out on a 50-metre square grid pattern, continuously from . the northern sector of 2008 drill program(2008 drilled site, DDH RRS08-34). With a practical mining stand point, there is no strong necessity to drill deeper than 168 meter (550 feet) per hole. The drill core sampling on regular 1.5 m sample interval should be confined to only ultramafic rocks.

17. STATEMENT OF COSTS

(Mainly based on the Company's audited 2008 Statement of Costs- Record Ridge South per Dwayne Vinck, C.A)

2008 Statement of Costs: Record Ridge South		
Expenses	Cost	Notes
Drilling (West Kootenay Drilling)	\$865,978	5,279 meters in NQ cores; \$165 per meter; West Kootenay, Castlegar, BC
Assays (Assayers Canada and ALS Chemex)	\$145,385	Multi-acid digested ICP, Fusion analysis Atomic absorption, PGM assays, etc.
Metallurgical Testing (Met-Solve lab.)	\$33,036	Metallurgical testing of bulk sample for recovery of magnesium
Freight of Samples to Laboratories	\$33,500	Westarm Overnight Trucking, Castlegar, BC
Surveying (Contractual)	\$35,200	Hango Land Surveyor, Castlegar, B C for the Surveyed line-grids and drill holes
Drill road building and Reclamation of drill sites	\$42,000	Brian Pistak, Excavation Contractor, Rossland, BC
NI 43-101 Resource Estimation	\$52,000	SRK Consulting Engineers & Scientists (Bart Stryhas, Ph.D) plus pit design
Wage/Personnel	\$244,909	
(Field Management \$24,000		\$3000/month x 8months
Consulting, supervision \$88,000		176 days @\$500 per day
Field geologist \$42,500		One men x 8.5 months@\$5,000 per month
One full time core splitter \$28,280		One men x 8 months@\$3,535 per month
Three part time core splitters \$33,840		3 men x 94 days x 6 hours/day @\$20 per hour
Full time water truck driver \$28,289)		One men x 8 months@\$3,536.13 per month
Meals and Accommodations	\$56,232	4 men x \$85.2 / day x 22 days / month x 7.5 months
Vehicle Expense	\$22,976	Insurance, fuel, storage and maintenance for three 4 x 4 trucks plus water truck: \$2,872 / month for 4 vehicles x 8 months
Travel	\$17,920	Two men(Consultant and Field Manager): 2 men x \$1,120/ man x 8 months
WCB BC	\$5,640	
Field Employees CPP & EI	\$5165	
Property and Mineral Taxes	\$2,685	
Total=	\$1,562,626	

18. REFERENCES

- Addie, G.G., (1973):** Geophysical Report on the “Job” Group of Claims, Rossland, Trail Creek Mining Division, British Columbia. British Columbia Assessment Report #4269, prepared for Mineral resources international Ltd., Calgary, AB.
- Andrew, K.P.E, Hoy, T., Simony, P.(1991):** Geology of the Trail Map Area,(82F/3,4,5,6): B.C. Ministry of Energy, Mines and petroleum Resources, open file 1991-16.
- Aparup,C (2007):** Mineralogical Investigation of Ivanhoe Ridge Drill Core Samples
- Drysdale, C.W., (1915):** Geology and Ore Deposits of Rossland, B.C. Geological Survey of Canada, Memoir 77,p.317
- Fyles, J.T. (1984).** Geological Setting of the Rossland Mining Camp. B.C. Ministry of Energy, Mines and petroleum Resources, Bulletin 74. p. 61
- Gilbert, G. (1984)** “Rossland Camp” in structural Geology of Canadian Ore Deposits (Jubilee Volume). Canadian Institute of Mining, p. 189-196
- Howe, A.C.A (1967);** Report on Midnight Mine Property. Report for Cinola Mines Ltd.
- Höy, T., Dunne, K.P.E. & Wehrle, D. (1992):** Tectonic and stratigraphic controls of gold-copper mineralization in the Rossland camp, Southeastern British Columbia (82F/4), British Columbia Geological Survey, paper 1992-1, p.261-272.
- Höy, T., Dunne, K.P.E. & Alldrick, D. (1998):** The relationship between intrusion-related Au-Cu sulphides veins and Mo breccias: Rossland. In: Metallogeny of Volcanic Arcs. British Columbia Geological Survey, short course notes. Open file 1998-8, section K.
- Höy, T., Dunne, K.P.E. (2001):** Metallogeny and mineral deposits of the Nelson-Rossland map area: Part II: The early Jurassic Rossland Group, Southeastern BC (82F/4). B.C. Ministry of Energy, Mines and petroleum Resources, Geological Survey Branch, Bulletin 109, p.196
- Höy, T., Dunne, K.P.E. (1997):** The early Jurassic Rossland Group, Southeastern British Columbia (82F/4). B.C. Ministry of Energy, Mines and petroleum Resources, Bulletin 102
- Höy, T., Dunne, K.P.E. (1998):** Geological compilation of the Trail map area, Southeastern B.C. (82F/3,4,5,5), B.C. Ministry of Energy, Mines and petroleum Resources, Geosciences map 1998-1.
- Leitch, C (2007):** Petrographic Reports on Drill Cores and Surface Samples on from W.H.Y. Resources’ Ivanhoe Ridge, Rossland, BC Project.
- Little, H.W. (1982):** Geology of the Rossland-Trail Map Area, British Columbia Geological Survey, 79-26, p.38.
- Morrison, L.G, White, A.M. (1979):** Geological, Geochemical & Geophysical Studies MAR 1-4, LAND 1-6, SKIN 1-4, ROSS & CAL claims, British Columbia assessment report #7162, prepared for United Canso Oil & Gas Ltd.

19. STATEMENT OF QUALIFICATION

I, Hun Kim, with a business address at 7555 Greenwood Street, Burnaby, BC do here certify that:

1. I am a consulting geologist and registered with the following professional organizations:
 - Association of Professional Engineers and Geoscientists of British Columbia (License #21179)
 - Association of Professional Engineers, Geologists and Geophysicists of Alberta (Life member registration #5848)
 - Geological Association Canada Fellow (Registration # F1309)
2. I am a graduate of Seoul National University(1958) holding B.ASc
3. During the period from 1969 to 1977, I have been a Mine Geologist and Chief Geologist of Granby Mining Company (daily production of 3,000 tonnes @0.88 % copper, 0.033 oz/t gold and 0.20 oz/t silver- Phoenix Open Pit and 19,000 tonnes @0.45 copper – Granisle Open), Project Engineer and Exploration Manager with Granby Mining Corporation Phoenix Copper Division(Phoenix Open Pit), Granisle Copper Ltd. and Zapata Granby Corporation(Houston, Texas).
4. I have been a geological engineer with British Columbia Hydro and Power Authority Thermal Power Division of Engineers Group, Vancouver, British Columbia from 1977 to 1983.
5. I have practiced my profession for 45 years in Canada, United States, Mexico, Africa and Far East Asia including China and Korea; including a professional service as an evaluation mining/geological engineer for seven years at U.S Agency of International Development per United Nations.
6. Since 1984, I have continued my geological engineering professional works as independent consultant domestically and internationally to the present.
7. I am currently working as Exploration Manager with West High Yield Resources. This assessment report was done without my bias, solely based on the exploration data of the property achieved and compiled to date.

January 28, 2009

H. Kim



Professional Seal


Statement of Qualification

I, Cory Peck, B.Sc., do hereby certify that:

- 1 I graduated from the University of Calgary with a B.Sc. in Geology in 2007.
- 2 I have worked as a field geologist with West high Yield Resources in Rossland, BC, since May 2007.
- 3 I am not aware of any faulty or misleading information contained within this assessment report.
- 4 I am a member in training with the Association of Professional Engineers, Geologists and Geophysicists of Alberta.

Dated this 28th day of January, 2009 Rossland, BC, Canada.

Respectfully submitted,

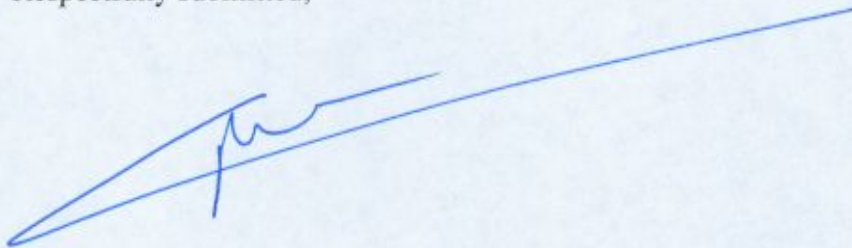A handwritten signature in blue ink, appearing to be 'Cory Peck', is written over a long, thin horizontal line.

Cory Peck, B.Sc.

APPENDIX I: Drilling results of 45 drill holes

(Geological core logs with grade compilation –Ni, Co, Cr,
Mg, and also selectively for Au, Ag and Pt.)

***Entire suite of drill logs can be found in attached file in digital format on
USB disk

APPENDIX II: 2008 assay File

***Entire suite of assay files can be found in attached file in digital format on
USB disk

**APPENDIX III: Two Metallurgical Test Reports by
Met-Solve Laboratories Inc.**

Magnesium Recovery from WHY Resources' samples
(September 17, 2008 & October 28, 2008)

***Entire suite of two metallurgical reports can be found in attached
file in digital format on USB disk

APPENDIX IV: Petrographic Analysis Reports of the Record Ridge Ultramafics

DIAMOND DRILL HOLE RECORD

PROPERTY:

RECORD RIDGE

DDH RRS07-1

DIP AND AZIMUTH TESTS			CORE SIZE: NQ	TOTAL DEPTH: 254.5 m	DATE STARTED: Oct. 20, 2007
DEPTH	ANGLE	AZIMUTH	HOLE ANGLE: -90°	HOLE AZIMUTH °	DATE FINISHED: Oct. 25, 2007
62.79m	-90°	089.3°	SECTION:	COLLAR ELEVATION:	ANALYSIS BY: Assayers Canada
124.05m	-89.4°	249.6°	GRID LOCATION: 1225W, 575S	RECOVERY:	LOGGED BY: H.K. & C.P.
151.18m	-89.7°	269.8°	UTM (NAD 83): 434677E 5432314N	CLAIM: Frank Sr. 3	CORE STORED AT: Midnight camp
245.97m	-89.4°	176.2°			

* Not assayed

DEPTH (meters) FROM TO		Recovery %	Description	Sample No.	FROM m	TO m	Length m	Ni ppm	Co ppm	Mg %	Fe ₃ O ₄ %	Cr %	Au g/t	Pt g/t	PD g/t
0	9.14	30	CASING												
9.14	9.34	100	SERPENTINITE Dark greenish-grey; highly fragmented												
9.34	14.2	100	ANDESITE Light greenish-grey; aphanitic; non-magnetic; strong; hard	42835 42836	9.34 11.74	11.74 14.2	2.4 2.46	94 85	37 37	* *	* *	* *	* *	* *	* *
14.2	18.22	100	SERPENTINITE Dark grey with crowded magnetite/chromite webs; strongly magnetic.	42837 42838 42839	14.2 15.67 17.17	15.67 17.17 18.22	1.47 1.5 1.05	2185 2315 2262	106 112 110	21.9 25.8 27.0	4.48 4.91 4.88	0.31 0.47 0.34	0.01 0.01 0.01	<0.01 <0.01 <0.01	<0.01 <0.01 <0.01
18.22	24.51	100	SERPENTINITE Jet-black type; strongly magnetic.	42840 42841 42842 42843	18.22 19.72 21.22 22.72	19.72 21.22 22.72 24.51	1.5 1.5 1.5 1.79	1910 2477 2235 1956	92 112 98 95	22.5 27.1 15.6 24.8	4.56 3.62 4.46 4.56	0.29 0.32 0.28 0.59	0.01 0.01 0.01 0.01	<0.01 <0.01 <0.01 <0.01	<0.01 <0.01 <0.01 <0.01
24.51	28.09	100	SERPENTINITE Dark grey with crowded magnetite/chromite webs; strongly magnetic.	42844 42845	24.51 26.01	26.01 28.09	1.5 2.07	2202 2368	108 111	25.0 25.0	4.06 4.19	0.72 0.31	0.02 0.02	<0.01 <0.01	<0.01 <0.01
28.09	32.41	100	SERPENTINITE Jet-black type; strongly magnetic.	42846 42847 42848	28.09 29.59 31.09	29.59 31.09 32.41	1.5 1.5 1.32	2355 2316 2389	113 104 114	27.3 27.6 27.3	4.17 4.88 4.93	0.36 0.45 0.36	0.07 0.01 0.01	<0.01 <0.01 <0.01	<0.01 <0.01 <0.01
32.41	33.61	100	SERPENTINITE Dark grey with crowded magnetite/chromite webs; strongly magnetic. Petrographic sample at 32.48 m Determined to be relict periotite(wehrlite?)	42849	32.41	33.61	1.2	2047	101	23.8	4.95	0.52	0.01	0.02	<0.01

[illegible]

[illegible]

DEPTH (meters) FROM TO		Recovery %	Description	Sample No.	FROM m	TO m	Length m	Ni ppm	Co ppm	Mg %	Fe ₃ O ₄ %	Cr %	Au g/t	Pt g/t	PD g/t
				42921	137.09	138.59	1.5	2148	110	24.7	4.55	0.27	*	*	*
				42922	138.59	141.09	2.5	1966	99	25.1	4.10	0.24	*	*	*
141.09	142.49	100	ANDESITE Light green; aphanitic; non-magnetic; richly pyritized.	42923	141.09	142.49	1.4	134	53	5.88	3.34	0.05	*	*	*
142.49	152.58	100	SERPENTINITE Jet-black type; strongly magnetic. 144.58-145.08m is pulverized serpentine 151.87m shows stress fractures oriented 45° to c.a., which run across a chrysotile vein 2 cm thick.	42924	142.49	143.99	1.5	2441	116	25.5	3.07	0.20	*	*	*
				42925	143.99	145.49	1.5	2533	122	20.1	2.58	0.35	*	*	*
				42926	145.49	146.99	1.5	2072	106	23.0	2.87	0.45	*	*	*
				42927	146.99	148.49	1.5	2100	109	24.6	2.71	0.35	*	*	*
				42928	148.49	149.99	1.5	2094	115	23.8	3.74	0.31	*	*	*
				42929	149.99	151.49	1.5	2215	118	23.1	4.28	0.41	*	*	*
				42930	151.49	152.58	1.09	2179	112	20.7	3.79	0.36	*	*	*
152.58	153.35	100	CHRYSTOLE SERPENTINITE Asbestos vein is 2-5 cm thick and 10° to c.a.	42931	152.58	153.35	0.77	2171	109	19.0	3.59	0.44			
153.35	155.2	100	SERPENTINITE Jet-black type; strongly magnetic; magnetite/ chromite webbing throughout.	42932	153.35	155.2	1.85	2153	118	19.7	3.04	0.31	*	*	*
155.2	156.53	100	TALCOSE-SILICIFIED ZONE Milky-white; compact; hard, but can be scratched readily; non-magnetic; no visual mineralization.	42933	155.2	156.53	1.33	27	30	3.03	2.89	0.01	*	*	*
156.53	157.7	100	ANDESITE Light green; weakly epidotized; lower contact is sharp and 70° to c.a.	42934	156.53	157.7	1.17	10	20	2.99	1.96	0.01	*	*	*
157.7	161.69	100	SERPENTINITE Jet-black type; strongly magnetic; magnetite/ chromite webbing throughout.	42935	157.7	159.17	1.47	2237	117	18.7	3.39	0.25	*	*	*
				42936	159.17	160.67	1.5	2202	114	22.9	4.37	0.42	*	*	*
				42937	160.67	161.69	1.02	2058	112	18.0	2.86	0.28	*	*	*
161.69	163.37	100	DIORITE Medium grained; equigranular; pronounced biotite flakes; strong; hard; weakly magnetic.	42938	161.69	163.37	1.68	162	49	5.74	2.43	0.09	*	*	*
163.37	167.54	100	SERPENTINITE Jet-black type; strongly magnetic.	42939	163.37	164.87	1.5	2284	114	23.0	5.29	0.42	*	*	*
				42940	164.87	166.37	1.5	2169	110	27.1	4.73	0.35	*	*	*
				42941	166.37	167.54	1.17	2085	101	22.7	4.19	0.47	*	*	*
167.54	168.93	100	PULVERIZED SERPENTINITE	42942	167.54	168.93	1.39	1326	68	20.6	3.86	0.21	*	*	*
168.93	179.40	100	SERPENTINITE Jet-black type; strongly magnetic.	42943	168.93	170.43	1.5	2240	109	26.5	4.89	0.43	*	*	*
				42944	170.43	171.93	1.5	2273	102	24.2	3.87	0.39	*	*	*
				42945	171.93	173.43	1.5	3569	185	23.1	3.50	0.31	*	*	*
				42946	173.43	174.93	1.5	6130	326	20.0	2.60	0.33	*	*	*
				42947	174.93	176.43	1.5	3984	210	22.2	2.93	0.24	*	*	*
				42948	176.43	177.93	1.5	2306	114	21.5	3.26	0.30	*	*	*

DEPTH (meters) FROM TO		Recovery %	Description	Sample No.	FROM m	TO m	Length m	Ni ppm	Co ppm	Mg %	Fe ₃ O ₄ %	Cr %	Au g/t	Pt g/t	PD g/t
				42949	177.93	179.40	1.47	1519	82	19.0	5.06	0.24	*	*	*
179.40	181.7	100	DIORITE TO GABBO-DIORITE Dark grey; coarse grained; equigranular; non-magnetic; conspicuous mafic grains.	42950	179.40	181.7	2.3	14	24	2.86	2.02	0.01	*	*	*
181.7	184.71	100	SERPENTINITE Green to dark green; soft; pulverized	42951 42952	181.7 183.16	183.16 184.71	1.46 1.55	258 1434	38 71	18.9 18.3	4.73 5.80	0.01 0.21	* *	* *	* *
184.71	195.25	100	SERPENTINITE Jet-black type; strongly magnetic.	42953 42954 42955 42956 42957 42958 42959	184.71 186.21 187.71 189.21 190.71 192.21 193.71	186.21 187.71 189.21 190.71 192.21 193.71 195.25	1.5 1.5 1.5 1.5 1.5 1.5 1.54	2120 2145 2152 2069 1969 2119 2070	121 119 132 111 107 129 120	22.9 25.8 24.3 25.8 22.5 24.3 21.7	4.05 4.30 3.77 3.69 3.40 3.91 3.54	0.31 0.31 0.26 0.33 0.33 0.23 0.24	* * * * * * *	* * * * * * *	* * * * * * *
195.25	198.51	100	CHRYSTOLE SERPENTINITE	42960 42961	195.25 196.88	196.88 198.51	1.63 1.63	1548 1360	82 78	19.6 19.2	3.11 2.76	0.18 0.17	* *	* *	* *
198.51	201.71	100	SERPENTINITE Jet-black type; strongly magnetic.	42962 42963	198.51 200.01	200.01 201.71	1.5 1.7	2004 1959	110 108	21.8 21.9	3.30 3.91	0.27 0.26	* *	* *	* *
201.71	204.60	100	SERPENTINITE Green to dark green; soft; pulverized; asbestos veinlets at random intervals; upper contact is sharp and 60° to c.a.; lower contact is broken.	42964 42965	201.71 203.21	203.21 204.60	1.5 1.39	1758 260	124 61	16.8 5.13	4.37 3.30	0.22 0.04	* *	* *	* *
204.60	231.23	100	GABBRO fine grained; predominately mafic minerals (augite, hornblende, biotite & amphiboles); equigranular; strong; hard; non-magnetic.	42966 42967 42968 42969 42970	204.60 206.60 208.60 210.60 212.60	206.60 208.60 210.60 212.60 214.60	2 2 2 2 2	16 40 62 10 31	35 39 39 20 34	* * * * *	* * * * *	* * * * *	* * * * *	* * * * *	* * * * *
231.23	234.85	100	SERPENTINITE Light green; soft; talcy; weakly magnetic.	42971 42972	231.23 233.04	233.04 234.85	1.81 1.81	339 1081	45 73	7.11 15.4	1.96 4.06	0.10 0.16	* *	* *	* *
234.85	237.9	100	BASALTIC ANDESITE Highly serpentinized; weakly magnetic.	42973 42974	234.85 236.35	236.36 237.9	1.51 1.55	26 523	35 59	2.5 13.7	2.35 3.16	0.01 0.06	* *	* *	* *
237.9	241.62	100	SERPENTINITE Light green; soft; talcy; weakly magnetic; lower contact is gradational.	42975 42976	237.9 239.75	239.75 241.62	1.85 1.87	1424 1859	87 100	14.3 18.7	2.83 3.13	0.15 0.18	* *	* *	* *
241.62	248.22	100	SERPENTINITE Jet black; aphanitic; strongly magnetic; lower contact is sharp and 65° to c.a.	42977 42978 42979 42980	241.62 243.12 244.62 246.12	243.12 244.62 246.12 248.22	1.5 1.5 1.5 2.1	2197 2201 2083 2173	114 112 115 117	27.5 28.2 25.3 28.1	2.81 2.31 2.36 3.07	0.25 0.16 0.27 0.21	* * * *	* * * *	* * * *
248.22	249.11	100	ANDESITE Light green; aphanitic; non-magnetic.	42981	248.22	249.11	0.89	35	42	4.31	3.95	0.02	*	*	*
249.11	250.04	100	SERPENTINITE	42982	249.11	251.52	2.41	1390	79	21.1	2.53	0.18	*	*	*

DEPTH (meters) FROM TO		Recovery %	Description	Sample No.	FROM m	TO m	Length m	Ni ppm	Co ppm	Mg %	Fe ₃ O ₄ %	Cr %	Au g/t	Pt g/t	PD g/t
			Jet-black type; strongly magnetic.												
250.04	251.52	100	SERPENTINIZED ANDESITE												
251.52	252.52	100	SERPENTINITE Light green; soft; talcy; weakly magnetic.	42983	251.52	252.52	1.0	1692	94	19.3	3.55	0.17	*	*	*
252.52	254.5	100	SERPENTINITE Jet-black type; strongly magnetic.	42984	252.52	254.5	1.98	2434	129	28.8	1.55	0.26	*	*	*

END OF HOLE

DIAMOND DRILL HOLE RECORD

PROPERTY:

RECORD RIDGE

DDH RRS07-2

DIP AND AZIMUTH TESTS			CORE SIZE: NQ	TOTAL DEPTH: 108.81 m	DATE STARTED: Oct. 25, 2007
DEPTH	ANGLE	AZIMUTH	HOLE ANGLE: -90°	HOLE AZIMUTH °	DATE FINISHED: Oct. 27, 2007
	90°		SECTION:	COLLAR ELEVATION:	ANALYSIS BY: Assayers Canada
	90°		GRID LOCATION: 1425W, 575S	RECOVERY:	LOGGED BY: H.K. & C.P.
			UTM (NAD 83): 434477E 5432314N	CLAIM: Hidden Valley 3	CORE STORED AT: Midnight camp

* Not assayed

DEPTH (meters) FROM TO		Recovery %	Description	Sample No.	FROM m	TO m	Length m	Ni ppm	Co ppm	Mg %	Fe ₃ O ₄ %	Cr %
0	1.57	30	CASING									
1.57	2.00	100	SURFACE BOULDERS									
2.00	5.03	100	SERPENTINITE Jet black; aphanitic; strongly magnetic; extremely fine-grained; <0.5mm nickel-sulphides looking minerals noted.	42985 42986	2.00 3.50	3.50 5.03	1.5 1.53	2153 2131	107 121	24.7 25.2	3.70 3.72	0.36 0.33
5.03	6.83	100	SERPENTINITE Dark green to black with greenish tone; contains several joints that have limonitized coatings. • 6.59-6.60m is fault gouged with coarse-grained sandy coating.	42987	5.03	6.83	1.80	2188	121	25.5	5.00	0.26
6.83	8.77	100	SERPENTINITE Jet black; aphanitic; strongly magnetic; extremely fine-grained; <0.5mm nickel-sulphides looking minerals noted.	42988	6.83	8.77	1.94	2129	112	26.3	4.30	0.29
8.77	12.75	100	SERPENTINITE Light green to dark green; moderately magnetic; thinly banded talcose stringers with green serpentine streaks. • 9.17-11.07m is jet-black serpentine.	42989 42990	8.77 11.02	11.02 12.75	2.25 1.73	2288 2203	124 117	25.9 25.1	4.55 4.30	0.36 0.28
12.75	19.8	100	SERPENTINITE Jet black; aphanitic; strongly magnetic; extremely fine-grained; <0.5mm nickel-sulphides looking minerals noted.	42991 42992 42993 42994 42995	12.75 14.25 15.75 17.25 18.75	14.25 15.75 17.25 18.75 19.8	1.5 1.5 1.5 1.5 1.07	2599 2344 2079 2102 2146	137 126 119 107 114	27.1 26.7 25.4 23.5 25.3	3.97 3.88 3.21 2.83 3.69	0.26 0.27 0.27 0.22 0.25

[illegible]

DEPTH (meters) FROM TO		Recovery %	Description	Sample No.	FROM m	TO m	Length m	Ni ppm	Co ppm	Mg %	Fe ₃ O ₄ %	Cr %
			Same as previously									
64.54	67.96	100	SERPENTINITE Dark grey to black with magnetite stockworks; strongly magnetic	43004 43005	64.54 66.04	66.04 67.98	1.5 1.94	2243 2396	117 122	20.3 19.8	2.00 1.70	0.27 0.20
67.96	69.80	100	SERPENTINITE Highly serpentinized basaltic andesite Fractures and joints are totally coated with serpentine	43006	67.98	69.80	1.82	1476	85	16.3	4.1	0.18
69.80	108.81	100	ANDESITE TO BASALT Same as previously End of Hole	43007 43008	69.80 72.24	72.24 74.24	2.44 2.00	51 18	36 18	* *	* *	* *

DIAMOND DRILL HOLE RECORD

PROPERTY:

Record Ridge South

DDH RRS07-3

DIP AND AZIMUTH TESTS			CORE SIZE: NQ	TOTAL DEPTH: 124m	DATE STARTED: October 28, 2007
DEPTH	ANGLE	AZIMUTH	HOLE ANGLE: -90°	HOLE AZIMUTH °	DATE FINISHED: October 29, 2007
63.09m	-88.5°	063.3°	SECTION:	COLLAR ELEVATION:	ANALYSIS BY: Assayers Canada
124.05m	-88.6°	327.2°	GRID LOCATION: 1325W, 575S	RECOVERY:	LOGGED BY: H.K. & C.P.
			UTM (NAD 83): 434577E 5432314N	CLAIM: Frank Sr. 3	CORE STORED AT: Midnight camp

* Not assayed ** assay in progress

DEPTH (meters) FROM TO		Reco ver %	Description	Sample No.	FROM m	TO m	Length m	Ni g/t	Co g/t	Mg %	Fe3O4 %	Cr %
0	9.14	100	CASING									
9.14	9.48		SURFACE BOULDERS Monzonite and green serpentine									
9.48	25.17	100	SERPENTINITE Dark grey to black; conspicuous stockwork of magnetite; thinly layered magnetite streaks 30° to c. a at random intervals; solid intact and strongly magnetic	43009 43010 43011 43012 43013 43014 43015 43016 43017 43018	9.48 10.98 12.48 13.98 15.48 16.98 18.48 19.98 21.48 22.98	10.98 12.48 13.98 15.48 16.98 18.48 19.98 21.48 22.98 25.17	1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 2.19	1998 1764 1566 2069 2160 2260 2191 2256 2168 2115	101 90 88 103 111 108 105 106 116 102	21.2 20.5 22.2 22.0 25.1 26.5 24.5 25.4 25.5 23.2	2.58 2.36 2.25 1.96 3.14 3.29 2.85 2.85 4.16 2.86	0.25 0.23 0.24 0.28 0.32 0.29 0.23 0.30 0.34 0.27
25.17	33.88		SERPENTINITE Jet black; strongly magnetic; lower contact is gradational.	43019 43020 43021 43022 43023 43024	25.17 26.67 28.17 29.67 31.17 32.67	26.67 28.17 29.67 31.17 32.67 33.88	1.5 1.5 1.5 1.5 1.5 1.21	2033 2274 2254 2235 2260 1960	100 111 109 112 108 90	25.1 30.4 27.8 29.4 28.4 25.0	3.32 4.71 4.05 4.21 3.97 3.30	0.28 0.33 0.31 0.42 0.39 0.25
33.88	36.21	100	SERPENTINITE Light to dark green; hard; compact; can be scratched; weakly to non-magnetic.	43025	33.88	36.21	2.33	1951	107	22.5	3.91	0.36
36.21	39.41	100	SERPENTINITE Jet black; strongly magnetic; upper contact is gradational; lower contact is faulted.	43026 43027	36.21 37.71	37.71 39.41	1.5 1.7	2192 1739	110 90	24.5 22.6	4.80 3.92	0.32 0.22
39.41	39.95	60	FAULT GOUGE Fragmented basalt and basaltic andesite.									
39.95	42.51	100	ANDESITE serpentinized; light green; aphanitic; non-	43028 43029	39.41 40.91	40.91 42.51	1.5 1.5	1307 68	78 30	16.5 3.51	5.06 3.26	0.18 0.01

DEPTH (meters) FROM TO		Reco ver %	Description	Sample No.	FROM m	TO m	Length m	Ni g/t	Co g/t	Mg %	Fe3O4 %	Cr %
			magnetic.									
42.51	43.51	100	SERPENTINITE Dark green; magnetite/ chromite stockworks.	43030	42.51	44.01	1.5	1713	91	24.1	6.04	0.3
43.51	50.73	100	SERPENTINITE Jet black; strongly magnetic.	43031 43032 43033 43034	44.01 45.51 47.01 48.51	45.51 47.01 48.51 50.73	1.5 1.5 1.5 2.22	2129 2163 2322 2243	111 114 119 111	24.8 25.1 24.5 23.0	5.22 5.68 4.67 4.50	0.27 0.28 0.27 0.28
50.73	54.85	100	SERPENTINITE Dark grey with pronounced magnetite/ chromite stockworks.	43035 43036 43037	50.73 52.23 53.73	52.23 53.73 54.85	1.5 1.5 1.12	1583 2179 2155	89 111 106	22.5 24.4 25.1	5.60 4.86 4.31	0.38 0.26 0.29
54.85	59.65	100	SERPENTINITE Grey with thin (1-2 mm) magnetite stockworks sporadically at 40° to c.a.; moderately magnetic;	43038 43039 43040	54.85 56.25 57.85	56.25 57.85 59.65	1.4 1.6 1.8	2290 2588 1603	114 123 85	26.1 25.8 22.6	4.34 4.63 5.33	0.28 0.36 0.21
59.65	60.15	100	SERPENTINITE Soft; talcy; green; pulverized.	43041	59.65	60.15	0.5	141	28	18.9	4.44	0.02
60.15	75.55	100	SERPENTINITE Greenish-grey; contains less prevalent magnetite stockworks; moderately to strongly magnetic. • 72.65-73.05 m is green serpentine.	43042 43043 43044 43045 43046 43047 43048 43049 43050 43051	60.15 61.65 63.15 64.65 66.15 67.65 69.15 70.65 72.15 73.0	61.65 63.15 64.65 66.15 67.65 69.15 70.65 72.15 73.0 75.55	1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 0.85 2.55	2103 1966 1499 1752 1719 1506 1785 1795 1539 1880	100 92 83 96 76 77 96 100 93 111	22.0 18.0 17.1 18.3 17.6 17.8 20.2 19.0 20.6 **	5.50 4.97 6.19 5.43 6.65 6.54 6.19 7.05 5.76 **	0.32 0.25 0.22 0.24 0.22 0.23 0.26 0.24 0.29 **
75.55	78.45	100	BASALTIC ANDESITE Strong; hard; non-magnetic	43052	75.55	78.45	2.9	94	39	*	*	*
78.45	82.30	100	SERPENTINITE Dark green; soft; weakly to non-magnetic.	43053 43054	78.45 80.45	80.45 82.30	2 1.85	1077 815	73 82	** **	** **	** **
82.30	85.64	100	BASALT TO BASALTIC ANDESITE Weakly serpentinized.	43055 43056	82.30 84.30	84.30 85.64	2 1.34	51 46	41 40	* *	* *	* *
85.64	86.18	100	SERPENTINE Green; pulverized.	43057	85.64	86.18	0.54	302	64	*	*	*
86.18	95.94	100	DIO-GABBRO TO GABBRO Black; coarse grained, phaneritic; non-magnetic.	43058 43059	86.18 88.18	88.18 90.18	2 2	297 353	51 58	* *	* *	* *
95.94	124.05	100	ANDESITE Light green; aphanitic; weakly magnetic. • 109.11-109.49m is a small quart vein with some rusted and mineralized vugs. • 115.80-117.40m is a highly	43060 43061 43062	95.94 109.11 115.80	97.94 109.49 117.40	2 0.3 1.6	40 24 16	44 24 39	* * *	* * *	* * *

DEPTH (meters) FROM TO		Reco ver %	Description	Sample No.	FROM m	TO m	Length m	Ni g/t	Co g/t	Mg %	Fe3O4 %	Cr %
			carbonitized area with heavy mineralization by galena, pyrite and possibly more.									

END OF HOLE

DIAMOND DRILL HOLE RECORD

PROPERTY:

Record Ridge South

DDH RRS07-4

DIP AND AZIMUTH TESTS			CORE SIZE: NQ	TOTAL DEPTH: 185.35m	DATE STARTED: October 29, 2007
DEPTH	ANGLE	AZIMUTH	HOLE ANGLE: -90°	HOLE AZIMUTH °	DATE FINISHED: November 5, 2007
59.74m	-88.7°	329.3°	SECTION:	COLLAR ELEVATION:	ANALYSIS BY: Assayers Canada
123.75m	-89.2°	298.7°	GRID LOCATION: 1125W, 575S	RECOVERY:	LOGGED BY: H.K. & C.P.
184.71m	-88.8°	342.7°	UTM (NAD 83): 434777E 5432314N	CLAIM: Frank Sr. 3	CORE STORED AT: Midnight camp

*Not assayed

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	Ni g/t	Co g/t	Mg %	Fe3O4 %	Cr %
0	2.13	100	CASING									
2.13	2.2		SURFACE BOULDERS									
2.2	6.52		SERPENTINITE Dark greenish-grey, moderately magnetic; plentiful talc stringers throughout; somewhat fragmented.	43063 43064 43065	2.2 3.75 5.25	3.75 5.25 6.52	1.55 1.5 1.27	2228 2162 2232	115 113 118	23.8 25.4 24.2	4.68 5.29 6.26	0.31 0.28 0.30
6.52	9.24		SERPENTINITE Greenish black; strongly magnetic; aphanitic; magnetite/ chromite webbing throughout; also somewhat fragmented.	43066 43067	6.52 8.02	8.02 9.24	1.5 1.22	2076 2167	103 110	23.6 23.8	5.00 5.82	0.29 0.30
9.24	13.75		SERPENTINITE Dark grey; moderately magnetic; magnetite/ chromite stringers 40° to c.a.; rusted in fractures with lots of talcy material as well.	43068 43069 43070	9.24 10.74 12.24	10.74 12.24 13.75	1.5 1.5 1.51	2400 2344 2418	116 123 120	23.7 23.2 25.4	6.52 6.22 5.69	0.36 0.25 0.29
13.75	71.93		SERPENTINITE Black to jet black; strongly magnetic; aphanitic; lower contact is broken but not faulted (without gouge).	43071 43072 43073 43074 43075 43076 43077 43078 43079 43080 43081 43082 43083 43084	13.75 15.25 16.75 18.25 19.75 21.25 22.75 24.25 25.75 27.25 28.75 30.25 31.75 33.25	15.25 16.75 18.25 19.75 21.25 22.75 24.25 25.75 27.25 28.75 30.25 31.75 33.25 34.75	1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5	2063 2245 2013 1965 1959 2136 2086 2266 2129 2280 2100 2102 2130 2037	105 104 105 109 111 115 118 116 115 121 111 111 109 108	23.1 23.6 23.5 27.9 29.2 27.9 27.3 31.8 29.2 27.0 28.4 31.8 32.5 27.8	4.27 4.59 4.59 5.61 4.95 4.86 5.87 6.52 6.33 6.38 5.65 6.76 6.19 5.97	0.34 0.26 0.32 0.29 0.44 0.50 0.53 0.49 0.40 0.33 0.49 0.42 0.30

DEPTH (meters) FROM TO		Reco ver %	Description	Sample No.	FROM m	TO m	Length m	Ni g/t	Co g/t	Mg %	Fe3O4 %	Cr %
				43085	34.75	36.25	1.5	2150	113	30.8	6.01	0.31
				43086	36.25	37.75	1.5	2266	117	30.8	6.47	0.79
				43087	37.75	39.25	1.5	2078	107	26.4	5.38	0.26
				43088	39.25	40.75	1.5	2067	107	26.7	5.60	0.26
				43089	40.75	42.25	1.5	2202	112	31.8	6.51	0.25
				43090	42.25	43.75	1.5	2143	112	25.6	4.92	0.23
				43091	43.75	45.25	1.5	2060	111	25.6	4.42	0.24
				43092	45.25	46.75	1.5	2158	113	29.5	5.11	0.41
				43093	46.75	48.25	1.5	2213	112	30.2	5.00	0.36
				43094	48.25	49.75	1.5	2299	121	24.4	4.57	0.23
				43095	49.75	51.25	1.5	2104	108	30.3	6.08	0.79
				43096	51.25	52.75	1.5	2263	119	32.3	6.38	0.49
				43097	52.75	54.25	1.5	2157	115	22.7	4.80	0.31
				43098	54.25	55.75	1.5	2150	108	22.2	3.72	0.26
				43099	55.75	57.25	1.5	2161	110	24.9	4.85	0.34
				43100	57.25	58.75	1.5	2264	110	26.7	5.90	0.32
				43101	58.75	60.25	1.5	2097	111	22.5	5.14	0.39
				43102	60.25	61.75	1.5	2129	111	24.4	5.21	0.38
				43103	61.75	63.25	1.5	2123	109	23.6	5.11	0.41
				43104	63.25	64.75	1.5	2125	108	23.3	4.82	0.37
				43105	64.75	66.25	1.5	1991	107	22.4	4.55	0.47
				43106	66.25	67.75	1.5	2042	110	24.1	5.43	0.40
				43107	67.75	69.25	1.5	2059	116	25.0	4.46	0.38
				43108	69.25	70.75	1.5	2041	115	20.9	4.60	0.31
				43109	70.75	71.93	1.18	2127	117	19.0	3.90	0.35
71.93	73.78		ANDESITE TO BASALTIC ANDESITE Moderately serpentinized.	43110	71.93	73.78	1.85	818	73	10.8	4.26	0.13
73.78	94.5		SERPENTINITE Black to jet black; strongly magnetic; aphanitic; upper contact is sharp, intrusive and 50-60° to c.a. • 81.08-82.22m is highly fragmented.	43111	73.78	75.28	1.5	2158	120	21.8	4.75	0.40
				43112	75.28	76.78	1.5	1876	110	21.2	3.77	0.32
				43113	76.78	78.28	1.5	2095	110	20.5	4.42	0.33
				43114	78.28	79.78	1.5	2224	111	21.5	3.65	0.28
				43115	79.78	81.08	1.3	2365	118	20.5	3.26	0.32
				43116	81.08	82.22	1.14	2180	108	21.6	3.73	0.38
				43117	82.22	83.72	1.5	1932	100	22.1	3.68	0.31
				43118	83.72	85.22	1.5	1944	102	19.8	3.28	0.31
				43119	85.22	86.72	1.5	1802	99	23.9	4.16	0.34
				43120	86.72	88.22	1.5	2063	110	25.5	5.28	0.38
				43121	88.22	89.72	1.5	2147	110	19.7	4.09	0.32
				43122	89.72	91.22	1.5	1935	97	22.4	3.99	0.32
				43123	91.22	92.72	1.5	2143	114	23.2	4.44	0.34
				43124	92.72	94.5	1.78	2134	109	24.1	4.46	0.32
94.5	109.9		DIORITE TO DIOGABBRO Fine to medium grained; greenish black	43125	94.5	96.57	2.07	58	35	*	*	*
				43126	96.57	98.57	2	39	36	*	*	*

DEPTH (meters) FROM TO		Reco ver %	Description	Sample No.	FROM m	TO m	Length m	Ni g/t	Co g/t	Mg %	Fe3O4 %	Cr %
				43127	98.57	100.57	2	29	37	*	*	*
				43128	100.57	102.57	2	21	32	*	*	*
				43129	102.57	104.57	2	19	31	*	*	*
				43130	104.57	106.57	2	392	50	*	*	*
				43131	106.57	108.57	2	40	45	*	*	*
				43132	108.57	109.9	1.33	294	54	*	*	*(
109.9	110.98		SERPENTINITE Light green; richly pyritized; mainly hard, but soft on some places.	43133	109.9	110.98	1.08	1162	77	25.2	5.25	0.21
110.98	118.4		SERPENTINITE Black to jet black; strongly magnetic; aphanitic.	43134	110.98	112.48	1.5	2082	111	32.2	5.98	0.40
				43135	112.48	113.98	1.5	2083	117	32.4	6.77	0.62
				43136	113.98	115.48	1.5	2231	114	34.5	5.94	0.29
				43137	115.48	116.98	1.5	2206	109	31.3	4.78	0.25
				43138	116.98	118.4	1.42	2156	112	30.5	5.07	0.68
118.4	123.4		DIORITE TO DIOGABBRO Fine to medium grained; greenish black; Both contacts are sharp and 70° to c.a.	43139	118.4	121.25	2.85	165	39	6.30	5.14	0.06
				43140	121.25	123.4	2.15	174	40	10.1	5.04	0.06
123.4	182.80	100	SERPENTINITE Black to jet black; strongly magnetic; aphanitic	43141	123.4	124.91	1.51	2137	116	32.8	5.67	0.32
				43142	124.91	126.41	1.5	2102	116	33.8	5.74	0.38
				43143	126.41	127.91	1.5	2146	118	33.9	5.86	0.35
				43144	127.91	129.41	1.5	2195	119	29.5	5.65	0.40
				43145	129.41	130.91	1.5	2068	119	30.3	4.88	0.35
				43146	130.91	132.41	1.5	2376	128	29.3	5.10	0.29
				43147	132.41	133.91	1.5	2098	120	28.1	4.44	0.25
				43148	133.91	135.41	1.5	2298	124	31.5	5.71	0.38
				43149	135.41	136.91	1.5	2067	110	26.1	4.13	0.26
				43150	136.91	138.41	1.5	2471	119	24.7	3.03	0.26
				43151	138.41	139.91	1.5	2333	125	24.2	3.23	0.23
				43152	139.91	141.41	1.5	2353	123	24.6	3.87	0.35
				43153	141.41	142.91	1.5	2204	116	24.7	3.87	0.28
				43154	142.91	144.41	1.5	2115	111	25.8	4.15	0.27
				43155	144.41	145.91	1.5	2236	120	26.8	4.37	0.33
				43156	145.91	147.41	1.5	2255	118	26.3	3.95	0.38
				43157	147.41	148.91	1.5	2251	110	25.2	3.16	0.24
				43158	148.91	150.41	1.5	2280	120	26.7	3.91	0.26
				43159	150.41	151.91	1.5	2204	121	25.1	4.12	0.48
				43160	151.91	153.41	1.5	2188	111	25.8	4.36	0.48
				43161	153.41	154.91	1.5	2067	102	25.8	3.51	0.30
				43162	154.91	156.41	1.5	2180	114	22.3	3.19	0.42
				43163	156.41	157.91	1.5	2049	106	23.4	3.33	0.31
				43164	157.91	159.41	1.5	2004	106	23.6	3.95	0.23
				43165	159.41	160.91	1.5	2119	111	22.3	3.46	0.28
				43166	160.91	162.41	1.5	2125	107	24.3	4.12	0.27

DEPTH (meters) FROM TO		Reco ver %	Description	Sample No.	FROM m	TO m	Length m	Ni g/t	Co g/t	Mg %	Fe3O4 %	Cr %
				43167	162.41	163.91	1.5	2263	113	25.9	4.38	0.35
				43168	163.91	165.41	1.5	2294	119	25.4	4.22	0.36
				43169	165.41	166.91	1.5	2233	115	22.6	3.68	0.28
				43170	166.91	168.41	1.5	2185	112	27.6	4.66	0.35
				43171	168.41	169.91	1.5	2029	109	26.1	5.21	0.30
				43172	169.91	171.41	1.5	2149	111	25.8	3.77	0.25
				43173	171.41	172.91	1.5	2400	118	21.9	4.31	0.25
				43174	172.91	174.41	1.5	2285	112	20.8	3.08	0.26
				43175	174.41	175.91	1.5	2088	107	21.4	4.16	0.29
				43176	175.91	177.41	1.5	1792	100	19.5	3.30	0.32
				43177	177.41	178.91	1.5	2269	107	20.3	3.36	0.23
				43178	178.91	180.41	1.5	2142	110	20.6	4.42	0.28
				43179	180.41	182.80	2.39	2354	120	21.1	4.98	0.36
182.80	183.20		FAULT GOUGE									
183.20	185.35		SERPENTINIZED ANDESITE Dark green; aphanitic; weakly magnetic; talcy.	43180	182.80	185.35	2.55	203	43	*	*	*

Hole was shut down at 185.35m, due to complications down the hole.

DIAMOND DRILL HOLE RECORD

PROPERTY:

Record Ridge South

DDH RRS07-5

DIP AND AZIMUTH TESTS			CORE SIZE: NQ	TOTAL DEPTH: 233.98m	DATE STARTED: November 7, 2007
DEPTH	ANGLE	AZIMUTH	HOLE ANGLE: -90°	HOLE AZIMUTH °	DATE FINISHED: November 12, 2007
62.8m	-89.9°	378.7°	SECTION:	COLLAR ELEVATION:	ANALYSIS BY: Assayers Canada
123.75m	-89.7°	028.2°	GRID LOCATION: 1225W, 675S	RECOVERY:	LOGGED BY: H.K. & C.P.
184.7m	-89.8°	066.2°	UTM (NAD 83): 434677E 5432214N	CLAIM: Frank Sr. 3	CORE STORED AT: Midnight camp
233.48m	-89.1°	356.6°			

* Not assayed

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	Ni g/t	Co g/t	Mg %	Fe3O4 %	Cr %
0	2.74	100	CASING									
2.74	3.34	60	BASALTIC ANDESITE Highly fragmented core	43181	2.74	3.34	0.8	737	58	*	*	*
3.34	3.5	50	FAULT GOUGE									
3.5	6.14	100	SERPENTINITE Dark green, compact hard (basaltic andesite looking)	43182 43183	3.5 4.88	4.88 6.14	1.34 1.26	2305 2225	115 111	19.9 20.3	4.91 3.97	0.30 0.29
6.14	8.08	40	SHEARED/ FAULTED ZONE in serpentinized basaltic andesite; highly fragmented and pulverized (excessive amount of g-stop fluid was used)	43184	6.14	8.08	1.94	1498	84	16.1	4.53	0.19
8.08	13.62	100	SERPENTINIZED BASALTIC ANDESITE/ DIORITE ; weakly magnetic; moderately strong and hard; but scratches fairly easily.	43185 43186 43187	8.08 10.97 12.47	10.97 12.47 13.62	2.89 1.5 1.15	703 150 275	75 45 53	14.2 16.7 14.1	5.53 4.92 5.29	0.09 0.02 0.04
13.62	29.06	100	SERPENTINITE Black to dark green; conspicuous stockworks of magnetite/ chromite; strongly magnetic.	43188 43189 43190 43191 43192 43193 43194	13.62 15.12 16.62 18.12 19.62 21.12 22.62	15.12 16.62 18.12 19.62 21.12 22.62 24.12	1.5 1.5 1.5 1.5 1.5 1.5 1.5	1885 2161 1348 1925 2086 2138 2315	105 110 85 96 105 106 119	18.4 20.0 17.0 15.3 20.6 21.4 21.1	4.73 6.00 4.63 1.87 3.83 3.26 3.88	0.24 0.26 0.27 0.23 0.23 0.28 0.27

DEPTH (meters) FROM TO		Reco ver %	Description	Sample No.	FROM m	TO m	Leng th m	Ni g/t	Co g/t	Mg %	Fe3O4 %	Cr %
				43195	24.12	25.62	1.5	2219	114	22.9	4.52	0.32
				43196	25.62	27.12	1.5	2165	114	23.3	4.48	0.26
				43197	27.12	29.06	1.94	2265	122	21.8	3.61	0.22
29.06	62.19	100	SERPENTINITE “Jet-Black” serpentinite.	43198	29.06	30.56	1.5	2164	119	22.0	4.15	0.23
				43199	30.56	32.06	1.5	2282	120	24.6	4.73	0.22
				43200	32.06	33.56	1.5	2194	118	22.8	4.84	1.88
				43201	33.56	35.06	1.5	2324	100	28.0	6.00	2.17
				43202	35.06	36.56	1.5	2518	123	24.7	5.06	0.31
				43203	36.56	38.06	1.5	2302	120	30.0	5.97	0.29
				43204	38.06	39.56	1.5	2250	118	26.8	5.97	0.27
				43205	39.56	41.06	1.5	2129	117	28.0	5.98	0.29
				43206	41.06	42.56	1.5	1966	111	24.4	5.29	0.26
				43207	42.56	44.06	1.5	2330	124	25.0	4.96	0.31
				43208	44.06	45.56	1.5	2316	124	23.8	4.23	0.28
				43209	45.56	47.06	1.5	2387	131	23.3	4.57	0.40
				43210	47.06	48.56	1.5	2415	128	25.2	5.42	0.28
				43211	48.56	50.06	1.5	2103	115	25.7	5.74	0.30
				43212	50.06	51.56	1.5	1241	88	17.5	4.60	0.10
				43213	51.56	53.06	1.5	771	68	19.5	8.04	0.18
				43214	53.06	54.56	1.5	2075	111	21.5	5.76	0.25
				43215	54.56	56.06	1.5	1569	92	21.9	5.24	0.20
				43216	56.06	57.56	1.5	2259	122	34.2	4.77	0.27
				43217	57.56	59.06	1.5	1948	109	21.5	4.56	0.36
43218	59.06	60.56	1.5	1151	84	17.0	5.17	0.30				
			43219	60.56	62.19	1.63	2259	119	23.9	4.78	0.34	
62.19	72.98	100	SERPENTINITE Black to dark green; conspicuous stockworks of magnetite/ chromite; strongly magnetic.	43220	62.19	63.69	1.5	2215	122	24.2	5.43	0.31
				43221	63.69	65.19	1.5	2112	118	25.6	5.97	0.46
				43222	65.19	66.69	1.5	2340	127	26.8	6.19	0.35
				43223	66.69	68.19	1.5	1951	106	23.9	4.56	0.29
				43224	68.19	69.69	1.5	2533	137	25.7	5.27	0.38
				43225	69.69	71.19	1.5	2274	123	27.0	5.54	0.43
				43226	71.19	72.98	1.79	2098	116	26.8	5.15	0.38
72.98	74.98	100	SERPENTINITE “Jet-Black” serpentinite.	43227	72.98	74.98	2	2023	117	25.3	5.69	0.36
74.98	75.44	100	BASALTIC ANDESITE; 0.46 m Aphanitic; megascopically porphyroblastic Included in sample 43228									
75.44	76.89	100	SERPENTINITE Black to dark green with magnetitite- chromite stockwork same as previously	43228	74.98	76.89	1.91	1626	100	21.8	5.57	0.28
76.89	77.12	100	BASALTIC ANDESITE; 0.23 m Aphanitic; weakly serpentized									

DEPTH (meters) FROM TO		Reco ver %	Description	Sample No.	FROM m	TO m	Leng th m	Ni g/t	Co g/t	Mg %	Fe3O4 %	Cr %
			Included in sample 43229									
77.12	79.11	100	SERPENTINITE Black to dark green; conspicuous stockworks of magnetite/ chromite; strongly magnetic.	43229	76.89	78.39	1.5	2192	126	23.6	4.41	0.33
79.11	80.21	100	SERPENTINITE Dark green; talcy asbestos veinlets parallel to c. a	43230	78.39	80.21	1.82	2093	112	23.9	4.71	0.33
80.21	83.29	100	SERPENTINITE "Jet-Black" serpentinite.	43231 43232	80.21 81.71	81.71 83.29	1.5 1.58	2227 2267	121 125	27.1 31.2	5.06 5.31	0.42 0.42
83.29	85.47	100	SERPENTINITE Whitish speckled black serpentinite; crowded talcy blebs, 3-5 mm with also magnetite stockworks	43233 43234	83.29 84.79	84.79 86.74	1.5 1.95	2392 2298	125 127	28.6 26.0	4.63 4.48	0.36 0.32
85.47	86.74	100	SERPENTINITE; 1.27 m Dark green; with talcy asbestos veinlets; sub-parallel to c.a. included in sample 43234									
86.74	90.58	100	SERPENTINITE "Jet-Black" serpentinite.	43235 43236 43237	86.74 88.24 89.74	88.24 89.74 90.58	1.5 1.5 0.84	2189 2352 2275	123 126 118	31.1 28.4 26.3	6.63 4.84 5.60	0.42 0.34 0.37
90.58	91.13	100	SERPENTINITE Dark green,compact hard (basaltic andesite looking)	43238	90.58	91.33	0.75	2074	109	23.5	4.89	0.36
91.13	91.33	100	SERPENTINIE; 0.2 m Green, talcy soft; pulverized Included in sample 43238									
91.33	97.14	100	SERPENTINITE Black to dark green; conspicuous stockworks of magnetite/ chromite; strongly magnetic.	43239 43240 43241 43242	91.33 92.83 94.33 95.83	92.83 94.33 95.83 97.14	1.5 1.5 1.5 1.31	2197 1951 2166 2263	115 106 118 121	26.5 25.7 26.9 26.7	5.29 5.00 5.47 4.99	0.36 0.27 0.32 0.35
97.14	97.91	100	SERPENTINITE; 1.27 m Dark green; with talcy asbestos veinlets	43243	97.14	97.91	0.77	2177	118	27.6	5.82	0.34
97.91	151.18		SERPENTINITE "Jet-Black" serpentinite. With sporadic magnetite webs(less than 10%) The overall cores are intact and solid except the following variations: Fragmented with serpentinitized fractures ; light green soapstone at:	43244 43245 43246 43247 43248 43249 43250 43251 43252 43253	97.91 99.41 100.91 102.41 103.91 105.41 106.91 108.41 109.91 111.41 112.91	99.41 100.91 102.41 103.91 105.41 106.91 108.41 109.91 111.41 112.91	1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5	2374 2269 2176 2255 2195 2479 2407 2500 2457 2419	124 122 117 122 118 135 131 129 126 133	29.5 28.3 25.0 31.1 28.0 29.5 32.0 31.1 30.2 32.1	6.36 6.84 5.00 6.88 5.15 6.77 6.69 7.37 6.72 6.19	0.38 0.30 0.29 0.41 0.30 0.39 0.43 0.53 0.46 0.35

DEPTH (meters) FROM TO		Reco ver %	Description	Sample No.	FROM m	TO m	Leng th m	Ni g/t	Co g/t	Mg %	Fe3O4 %	Cr %
			123.0 m – 123.75 m 124.6 m – 125.0 m 126.8 m – 130.6 m 138.8 m -- 139.1 m 140.0 m – 140.3 m 140.53m – 148.13 m (Also contains gypsum crystals)	43254 43255 43256 43257 43256 43259 43260 43261 43262 43263 43264 43265 43266 43267 43268 43269 43270 43271 43272 43273 43274 43275 43276 43277 43278	112.91 114.41 115.91 117.41 118.91 120.41 121.91 123.41 124.91 126.41 127.91 129.41 130.91 132.41 133.91 135.41 136.91 138.41 139.91 141.41 142.91 144.41 145.91 147.41 148.91	114.41 115.91 117.41 118.91 120.41 121.91 123.41 124.91 126.41 127.91 129.41 130.91 132.41 133.91 135.41 136.91 138.41 139.91 141.41 142.91 144.41 145.91 147.41 148.91	1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 2.27	2262 2467 2320 2504 2508 2303 2022 1789 1866 2087 1944 1844 2205 2253 2311 2163 2107 2186 2215 2378 2338 2266 2198 1444 2091	124 130 124 132 131 121 112 97 111 111 104 105 115 115 124 124 109 112 116 123 126 128 125 93 112	33.9 33.6 31.6 30.8 29.5 29.2 30.6 27.7 25.3 23.7 23.8 26.1 27.7 26.9 28.2 27.2 28.0 26.2 27.2 26.5 26.9 28.8 26.9 24.2 27.4	7.46 7.66 7.37 6.83 7.78 6.54 6.51 4.10 5.42 5.68 4.20 4.57 5.61 5.69 6.11 5.85 6.11 5.89 5.21 3.79 3.79 4.67 6.26 7.02 4.68	0.27 0.39 0.37 0.46 0.37 0.35 0.33 0.23 0.30 0.28 0.26 0.28 0.29 0.31 0.30 0.33 0.31 0.30 0.32 0.26 0.26 0.26 0.26 0.17 0.26
151.18	152.58		SERPENTINIZED BASALTIC ANDESITE Weakly to moderately serpentinized; weakly to non-magnetic; megascopically porphyritic; fine-grained.	43279	151.18	152.58	1.4	1088	76	20.4	7.10	0.16
152.58	154.23		SERPENTINITE Black with magnetite/ chromite webbing.	43280	152.58	154.23	1.65	2323	128	21.6	8.46	0.28
154.23	156.13		SERPENTINIZED DIORITE Weak ly to moderately serpentinized; weakly to non-magnetic; megascopically porphyritic; fine-grained.	43281	154.23	155.73	1.5	956	74	22.5	5.93	0.12
156.13	170.2		SERPENTINITE Black with sporadic (<20%) magnetite/ chromite stockworks.	43282 43283 43284 43285 43286 43287 43288 43289 43290	155.73 157.23 158.73 160.23 161.73 163.23 164.73 166.23 167.73	157.23 158.73 160.23 161.73 163.23 164.73 166.23 167.73 170.2	1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 2.47	2153 2124 2305 2250 2079 1593 2357 2242 2029	114 115 125 123 110 94 123 119 111	26.8 26.2 27.6 29.1 27.1 22.0 25.6 26.1 25.2	4.45 3.52 4.81 5.06 4.57 4.74 4.24 4.21 5.21	0.31 0.33 0.22 0.30 0.23 0.25 0.23 0.27 0.32

DEPTH (meters) FROM TO		Reco ver %	Description	Sample No.	FROM m	TO m	Leng th m	Ni g/t	Co g/t	Mg %	Fe3O4 %	Cr %
170.2	197.6		DIOGABBRO Medium to coarse-grained.	43291	170.2	172.22	2.02	48	26	*	*	*
				43292	172.22	174.22	2	140	37	*	*	*
				43293	174.22	176.22	2	34	31	*	*	*
				43294	176.22	178.22	2	35	38	*	*	*
				43295	178.22	180.22	2	37	49	*	*	*
				43296	180.22	182.22	2	29	36	*	*	*
				43297	182.22	184.22	2	14	30	*	*	*
				43298	184.22	186.22	2	12	29	*	*	*
				43299	186.22	188.22	2	21	43	*	*	*
				43300	188.22	190.22	2	25	33	*	*	*
				43301	190.22	192.22	2	32	27	*	*	*
				43302	192.22	194.22	2	12	27	*	*	*
				43303	194.22	197.6	3.38	27	30	*	*	*
197.6	210.1		SERPENTINE Light green to green talcy soapstone; weakly to non-magnetic.	43304	197.6	199.13	1.53	1627	89	20.0	5.50	0.25
				43305	199.13	200.63	1.5	1842	93	26.8	4.81	0.29
				43306	200.63	202.13	1.5	1239	79	19.9	5.68	0.20
				43307	202.13	203.63	1.5	954	63	15.2	4.67	0.14
				43308	203.63	205.13	1.5	1013	64	16.9	5.35	0.15
				43309	205.13	206.63	1.5	1380	80	21.3	6.61	0.27
				43310	206.63	208.13	1.5	1381	77	16.8	4.57	0.22
				43311	208.13	210.1	1.97	1500	79	21.5	6.95	0.25
210.1	217.33		DIOGABBRO Medium to coarse-grained.	43312	210.1	212.12	2.02	66	33	*	*	*
				43313	212.12	214.12	2	74	36	*	*	*
				43314	214.12	217.33	3.21	37	34	*	*	*
217.33	219.67		SERPENTINE Dark green with serpentized diogabbro; weakly magnetic.	43315	217.33	219.67	2.34	1867	96	*	*	*
219.67	233.98		DIOGABBRO Medium to coarse-grained.	43316	219.67	221.67	2	48	37	*	*	*
				43317	221.67	223.67	2	56	35	*	*	*
				43318	223.67	225.67	2	54	33	*	*	*
				43319	225.67	227.67	2	8	32	*	*	*
				43320	227.67	229.67	2	11	25	*	*	*
				43321	229.67	231.67	2	8	23	*	*	*
				43322	231.67	233.98	2.31	160	36	*	*	*

END OF DDH RRS07-5

DIAMOND DRILL HOLE RECORD

PROPERTY:

Record Ridge South

DDH RRS07-6

DIP AND AZIMUTH TESTS			CORE SIZE: NQ	TOTAL DEPTH: 224.33 m	DATE STARTED: November 13, 2007
DEPTH	ANGLE	AZIMTH	HOLE ANGLE: -90°	HOLE AZIMUTH °	DATE FINISHED: November 17, 2007
63 m	-89.4°	112°	SECTION:	COLLAR ELEVATION:	ANALYSIS BY: Assayers Canada
124 m	-89.5°	162°	GRID LOCATION: 1125W, 675S	RECOVERY:	LOGGED BY: H.K. & C.P.
184 m	-89.5°	353°	UTM (NAD 83): 434777E 5432214N	CLAIM: Frank Sr. 3	CORE STORED AT: Midnight camp
224 m	-89.5°	292°			

*Not assayed

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	Ni g/t	Co g/t	Mg %	Fe3O4 %	Cr %
0		100	CASING									
2.74	3.9		SURFACE ROCKS Sub-rounded and angular fragments of rusted, dark-green dunite.									
3.9	41.15	100	SERPENTINITE Black with slight greenish tinge; aphanitic; strongly magnetic. 10.99-11.42m is greenish grey and rusted. 14.72-16.92m is greenish grey and rusted.	43323	3.9	5.43	1.53	2342	120	23.9	6.26	0.25
				43324	5.43	6.93	1.5	2180	103	23.9	4.91	0.18
				43325	6.93	8.43	1.5	2133	111	25.9	6.15	0.28
				43326	8.43	9.93	1.5	2367	110	24.6	6.90	0.19
				43327	9.93	11.43	1.5	2213	110	23.1	5.98	0.17
				43328	11.43	12.93	1.5	2378	133	24.9	5.85	0.19
				43329	12.93	14.72	1.79	2095	117	25.9	5.83	0.34
				43330	14.72	16.92	2.2	2034	102	23.5	5.21	0.30
				43331	16.92	18.42	1.5	2028	105	21.8	4.88	0.22
				43332	18.42	19.92	1.5	2110	114	24.4	4.64	0.18
				43333	19.92	21.42	1.5	1747	104	24.9	6.26	0.20
				43334	21.42	22.92	1.5	2114	118	25.0	5.39	0.19
				43335	22.92	24.42	1.5	2065	119	25.1	6.07	0.37
				43336	24.42	25.92	1.5	2091	110	26.5	5.83	0.30
				43337	25.92	27.42	1.5	2252	123	26.9	6.25	0.17
				43338	27.42	29.92	1.5	2082	112	25.3	5.93	0.30
				43339	29.92	31.42	1.5	1997	108	27.6	5.15	0.33
				43340	31.42	32.92	1.5	405	55	20.7	5.58	0.08
				43341	32.92	34.42	1.5	1885	133	25.0	6.61	0.30
				43342	34.42	35.92	1.5	2117	119	26.0	5.90	0.24
				43343	35.92	37.42	1.5	2017	108	26.5	6.85	0.32

DEPTH (meters) FROM TO		Reco ver %	Description	Sample No.	FROM m	TO m	Leng th m	Ni g/t	Co g/t	Mg %	Fe3O4 %	Cr %
				43344	37.42	38.92	1.5	2160	93	27.4	6.19	0.29
				43345	38.92	41.15	2.23	2322	109	24.4	6.33	0.20
41.15	42.35	100	SERPENTINE Mixed with serpentinitized andesite; weak to non-magnetic.	43346	41.15	42.35	1.2	334	55	17.6	6.12	0.03
42.35	46.40	100	SERPENTINITE Black with slight greenish tinge; aphanitic; strongly magnetic.	43347	42.35	43.85	1.5	2344	86	25.0	4.34	0.18
				43348	43.85	45.35	1.5	2375	86	26.5	4.99	0.24
				43349	45.35	46.40	1.05	2172	94	26.2	5.02	0.22
46.40	48.29	100	SERPENTINITE Sheared; rusted & green.	43350	46.40	48.29	1.89	2274	98	26.1	5.15	0.45
48.29	56.97	100	SERPENTINITE Jet black, strongly magnetic.	43351	48.29	49.79	1.5	2256	91	26.7	6.03	0.76
				43352	49.79	51.29	1.5	2390	111	26.0	5.64	0.23
				43353	51.29	52.79	1.5	2420	126	27.2	6.41	0.31
				43354	52.79	54.29	1.5	2423	124	29.4	6.98	0.30
				43355	54.29	55.79	1.5	2077	102	28.8	6.44	0.29
				43356	55.79	56.97	1.18	1249	75	21.3	6.03	0.26
56.97	59.0	100	SHEARED/FAULTED ZONE in serpentinite Gouged, pulverized serpentinite; black serpentinite and serpentine; also contains fragments of basaltic andesite.	43357	56.97	59.0	2.03	1563	74	22.6	6.34	0.36
59.0	70.68	100	DIORITE TO DIOGABBRO Black; lower contact is sharp and fault gouged at 65° to c.a.; medium grained; crowded with biotite and amphiboles (almost pyroxenite looking).	43358	59.0	60.99	1.99	102	47	*	*	*
				43359	60.99	62.99	2	49	42	*	*	*
				43360	62.99	64.99	2	42	41	*	*	*
				43361	64.99	66.99	2	34	41	*	*	*
				43362	66.99	68.99	2	21	34	*	*	*
				43363	68.99	70.68	1.69	50	35	*	*	*
70.68	73.66	100	SHEARED/FAULT ZONE • 40% fault gouge • 60% green, talcy soapstone and serpentine.	43364	70.68	71.93	1.25	1323	91	*	*	*
				43365	71.93	73.66	1.73	1092	75	*	*	*
73.66	82.5	100	DIORITE TO DIOGABBRO	43366	73.66	75.66	2	298	55	*	*	*
				43367	75.66	77.66	2	324	57	*	*	*
				43368	77.66	79.66	2	379	61	*	*	*
				43369	79.66	82.5	2.84	341	57	*	*	*
82.5	82.83	100	SERPENTINE Green soapstone; lower contact is 70° to c.a.	43370	82.5	83.62	1.12	1773	93	26.6	6.22	0.22
82.83	83.62	100	SERPENTINITE Dark green. (Included in sample 43370)									
83.62	96.00	100	SERPENTINITE Jet black, strongly magnetic; aphanitic	43371	83.62	85.12	1.5	2315	119	28.9	6.73	0.26
				43372	85.12	86.62	1.5	2308	122	29.6	7.14	0.27
				43373	86.62	88.12	1.5	2269	120	30.2	7.12	0.26
				43374	88.12	89.62	1.5	2449	128	32.2	8.17	0.27

DEPTH (meters) FROM TO		Reco ver %	Description	Sample No.	FROM m	TO m	Leng th m	Ni g/t	Co g/t	Mg %	Fe3O4 %	Cr %
				43375	89.62	91.12	1.5	2337	120	25.8	6.76	0.24
				43376	91.12	92.62	1.5	2221	114	29.0	4.77	0.27
				43377	92.62	94.12	1.5	2284	114	28.4	4.95	0.31
				43378	94.12	96.00	1.88	2006	112	28.8	4.68	0.26
96.00	99.86	100	DIOGABBRO TO GABBRO Coarse-grained; weakly to non-magnetic.	43379	96.00	98.00	2	617	60	13.5	3.40	0.12
				43380	98.00	99.9	1.9	368	64	10.6	4.08	0.11
99.9	105.7	100	SERPENTINITE Jet black, strongly magnetic; aphanitic	43381	99.86	101.36	1.5	2193	116	29.3	5.51	0.27
				43382	101.36	102.86	1.5	2303	124	30.6	5.11	0.29
				43383	102.86	104.36	1.5	2365	128	27.7	4.52	0.23
				43384	104.36	105.7	1.34	2136	115	27.7	5.24	0.25
105.7	115.20	100	DIOGABBRO TO GABBRO Coarse-grained; weakly to non-magnetic.	43385	105.72	107.72	2	497	65	*	*	*
				43386	107.72	109.72	2	332	57	*	*	*
				43387	109.72	111.72	2	387	63	*	*	*
				43388	111.72	113.72	2	336	60	*	*	*
				43389	113.72	115.20	1.48	353	58	*	*	*
115.20	116.20	100	SERPENTINITE Dark green with talcy soapstone.	43390	115.20	116.20	1	2179	113	24.8	2.98	0.22
116.20	118.20	100	DIOGABBRO TO GABBRO Coarse-grained; weakly to non-magnetic.	43391	116.20	118.20	2	391	62	7.43	3.66	0.12
118.20	120.09		SERPENTINIZED DIAGABBRO	43392	118.20	120.09	1.89	1237	88	19.2	3.94	0.19
120.09	122.40	100	SERPENTINITE Jet black, strongly magnetic; aphanitic	43393	120.09	122.40	2.31	2177	105	26.7	4.35	0.31
122.40	124.20	100	SERPENTINITE Black with pronounced magnetite webs and soapstone coated fractures.	43394	122.40	124.20	1.8	1681	86	26.1	5.86	0.41
124.20	130.5	100	SERPENTINITE Black; solid; pronounced magnetite webs; lower contact is sharp and 60° to c.a. and filled with soapstone.	43395	124.20	125.70	1.5	2151	100	23.8	4.59	0.37
				43396	125.70	127.20	1.5	2125	102	25.3	4.66	0.33
				43397	127.20	128.70	1.5	2161	99	28.1	5.31	0.37
				43398	128.70	130.5	1.8	1897	88	22.2	4.30	0.39
130.5	134.8	100	DIOGABBRO TO GABBRO Coarse-grained; weakly to non-magnetic.	43399	130.5	132.48	1.98	392	47	10.1	3.73	0.14
				43400	132.48	134.8	2.32	352	47	8.70	2.83	0.28
134.8	141.32	100	SERPENTINITE Jet black, strongly magnetic; aphanitic	43401	134.8	136.28	1.48	2200	117	23.9	3.74	0.26
				43402	136.28	137.78	1.5	2247	116	26.2	5.02	0.36
				43403	137.78	139.28	1.5	2109	111	23.9	5.03	0.28
				43404	139.28	141.32	2.04	1895	108	24.6	4.75	0.37
141.32	142.70	100	SERPENTINITE Dark grey with magnetite webs.	43405	141.32	142.70	1.38	1986	108	25.3	6.43	0.29
142.70	147.78	100	SERPENTINIZED DIAGABBRO Talcy green serpentine mixed with diogabbro..	43406	142.70	144.20	1.5	1269	83	*	*	*
				43407	144.20	145.70	1.5	1265	83	*	*	*
				43408	145.70	147.78	2.08	1050	83	*	*	*
147.78	196.80	100	DIOIRITE TO DIAGABBRO Medium to coarse grained; weak to non-magnetic; compact hard'	43409	147.78	149.78	2	41	43	*	*	*
				43410	149.78	151.78	2	64	57	*	*	*
				43411	151.78	153.78	2	42	49	*	*	*

DEPTH (meters) FROM TO		Reco ver %	Description	Sample No.	FROM m	TO m	Leng th m	Ni g/t	Co g/t	Mg %	Fe3O4 %	Cr %
			165.0 – 165.42: fractures are filled with soapstone: 177.62 – 178.21: Same as above	43412 43413 43414 43415 43416 43417 43418 43419 43420 43421 43422 43423 43424 43425 43426 43527 43428 43429 43430 43431 43432 43433	153.78 155.78 157.78 159.78 161.78 163.78 165.78 167.78 169.78 171.78 173.78 175.78 177.78 179.78 181.78 183.78 185.78 187.78 189.78 191.78 193.78 195.78	155.78 157.78 159.78 161.78 163.78 165.78 167.78 169.78 171.78 173.78 175.78 177.78 179.78 181.78 183.78 185.78 187.78 189.78 191.78 193.78 195.78	2 2 2 2 2 2 2 2 2 2 2 2 2 2 2 2 2 2 2 2 2 2 2	22 33 25 27 26 23 31 20 20 21 15 18 14 18 17 21 109 134 31 63 36 23	41 40 34 36 37 35 38 38 35 37 35 37 34 34 34 38 45 60 41 40 35 40	* *	* *	* *
196.80	198.12	100	SERPENTINE Light green to dark green; solid intact but being readily scratched; weak to non-magnetic	43434	196.80	198.42	1.62	111	38	*	*	*
198.12	198.42	100	CALCITE VEIN Snow white; barren looking; lower contact is pulverized in soapstone Included in sample 43435									
198.42	204.00	100	SERPENTINE Dark green to green same as previously	43435 43436 43437	198.42 199.92 201.42	199.92 201.42 204.00	1.5 1.5 2.58	451 138 425	89 53 51	* * *	* * *	* * *
204.00	207.00	100	DIAGABBRO Serpentinized; lower contact 30° to c.a.	43438 43439	204.00 205.5	205.5 207.0	1.5 1.5	142 120	39 35	* *	* *	* *
207.00	209.44	100	SERPENTINE Dark green to green same as previously	43440 43441	207.00 208.5	208.5 209.44	1.5 0.94	193 120	32 42	* *	* *	* *
209.44	210.82	100	LISTWANIZED SERPENTINITE Highly carbonatized and kaolinized; bleached white coloration mixed with green serpentinite; moderately mineralized (mainly pyrite up to 10 %); lower contact gradational	43442	209.44	210.82	1.38	1788	102	*	*	*
210.82	214.29	100	SERPENTIITE	43443	210.82	212.32	1.5	2158	121	*	*	*

DEPTH (meters) FROM TO		Reco ver %	Description	Sample No.	FROM m	TO m	Leng th m	Ni g/t	Co g/t	Mg %	Fe3O4 %	Cr %
			Dark green to greenish black; moderately magnetic; aphanitic without visual calcite-magnetite stockwork	43444	212.32	214.29	1.97	888	69	*	*	*
214.29	216.50	100	DIAGABBRO Serpentinized	43445	214.29	216.50	2.21	42	37	*	*	*
216.50	221.48		SERPENTIITE Dark green with calcite-magnetite stockwork at random intervals	43446 43447 43448	216.50 218.0 219.5	218.0 219.5 221.48	1.5 1.5 1.98	2150 2024 1993	120 101 107	* * *	* * *	* * *
221.48	223.45	100	BRECCIATED LISTWANITE Crowded green serpentine to serpentinite breccias, up to 5 cm in carbonatized(calcitic) and kaolinized serpentine; lower contact in green soapstone	43449	221.48	223.45	1.97	1816	93	*	*	*
223.45	224.33	100	BASALTIC ANDESITE TO DIAGABBRO End of Hole	43450	223.45	224.33	0.88	385	39	*	*	*

DIAMOND DRILL HOLE RECORD

PROPERTY:

RECORD RIDGE SOUTH

DDH RRS08- 1

DIP AND AZIMUTH TESTS			CORE SIZE: NQ	TOTAL DEPTH: 122.8m	DATE STARTED May 29, 2008
DEPTH	ANGLE	AZIMUTH	HOLE ANGLE: - 90°	HOLE AZIMUTH °	DATE FINISHED: June 2, 2008
122.8m	-88°	000°	SECTION:	COLLAR ELEVATION: 1445.2 m	ANALYSIS BY: Assayers Canada
			GRID LOCATION: 525 S / 1225 W	RECOVERY:	LOGGED BY: H.K. & C.P.
			UTM (NAD 83): 5432364 N 434677E	CLAIM: Frank Sr. 3	CORE STORED AT: Midnight camp

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	Ni ppm	Co ppm	Mg %	Cr %
0	1.8		Casing to 1.8 m								
1.8	2.6	60	Weakly serpentinitized TRACHYANDESITE (?) Light greenish grey to pink grey; Fine to aphanitic; porphyritic textured; euhedral to subeudral (rectangular) feldspar 2 – 3 mm and mafics (biotite, hornblende or probably pyroxene) in a fine-grained to aphanitic groundmass; moderately broken	43451	0	2.6	2.6	1409	68	13.21	0.24
2.6	15.4	70	SERPENTINITE Dark grey to black; weakly banded and streaked; Moderately broken ; magnetite-chromite 45° to CA\ Poor core recovery at 4.1- 7.1 (<50%)	43452 43453 43454 43455 43456 43457 43458	2.6 4.1 7.1 8.6 10.4 12.5 14	4.1 7.1 8.6 10.4 12.5 14 15.4	1.8 3 1.5 1.8 2.1 1.5 1.4	3208 2655 2383 2338 2463 2285 2300	137 134 108 94 106 92 94	24.66 24.60 25.86 25.28 26.40 23.84 21.33	0.31 1.95 0.34 0.27 0.26 0.26 0.31
15.4	16.6	100	RUSTED SERPENTINITE Moderately fragmented; highly limonitized; weakly magnetic	43459	15.4	16.6	1.2	1229	77	18.67	0.18
16.6	18.6	100	SERPENTINITE Light green grey; Moderately listwanized; weakly magnetic; talc-carbonaceous blebs and streaks up to 10%	43460	16.6	18.6	2	1602	76	18.26	0.18
18.6	19.6	100	SERPENTINIITE Absolute black; homogeneously black; Magnetic	43461	18.6	19.6	1	2201	99	19.97	0.19
19.6	25.9	100	ANDESITE Light green to grey; apnanitic; strong hard cores; weakly magnetic; intervened serpentinitized sections at random intervals	43462 43463 43464	19.6 21.6 23.6	21.6 23.6 25.9	2 2 2.3	426 851 27	24 44 20	6.10 12.28 6.08	0.03 0.04 0.02

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	Ni ppm	Co ppm	Mg %	Cr %
25.9	28.9	100	MIXED LIGHT GREY LISTWANIZED SERPENTINE	43465 43466	25.9 27.4	27.4 28.9	1.5 1.5	1969 1848	94 87	17.41 7.62	0.33 0.01
28.9	30.8	100	ANDESITE Lower contact is sharp and 40° to c.a.	43467	28.9	30.8	1.9	54	48	14.38	0.28
30.8	36.8	100	SERPENTINIITE Absolute black; homogeneously black; Magnetic, lower contact is gradational.	43468 43469 43470 43471	30.8 32.3 33.8 35.3	32.3 33.8 35.3 36.8	1.5 1.5 1.5 1.5	2387 2359 2380 1791	107 120 109 90	23.42 23.91 25.01 20.97	0.31 0.34 0.41 0.29
36.8	39.2	100	SERPENTINITE Milky-white type, weakly magnetic	43472 43473	36.8 38.0	38.0 39.2	1.2 1.2	1797 630	77 51	17.63 9.93	0.15 0.07
39.2	41.9	100	SERPENTINITE Light green, silky, upper & lower contacts are gradational.	43474 43475	39.2 40.6	40.6 41.9	1.4 1.3	1248 1836	68 88	15.00 20.27	0.23 0.28
41.9	64.4	100	SERPENTINIITE Absolute black; homogeneously black; Magnetic; without visible listwanization	43476 43477 43478 43479 43480 43481 43482 43483 43484 43485 43486 43487 43488 43489 43490	41.9 43.4 44.9 46.4 47.9 49.4 50.9 52.4 53.9 55.4 56.9 58.4 59.9 61.4 62.9	43.4 44.9 46.4 47.9 49.4 50.9 52.4 53.9 55.4 56.9 58.4 59.9 61.4 62.9 64.4	1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5	2378 2330 2321 2282 2182 2494 2480 2460 2456 2535 2346 2615 2548 2662 2251	113 106 104 109 106 129 141 125 149 162 141 140 148 142 98	23.35 26.29 24.99 26.10 25.83 27.38 26.49 27.39 28.66 28.29 27.27 28.47 27.31 27.59 24.53	0.34 0.29 0.29 0.36 0.37 0.28 0.40 0.22 0.28 0.35 0.32 0.27 0.29 0.31 0.32
64.4	68.9	100	SERPENTINITE Dark grey to black; listwanized; talcy- carbonaceous webs throughout; Lower 1.5 m section gradationally changes to light green soft serpentinite	43491 43492 43493	64.4 65.9 67.4	65.9 67.4 68.9	1.5 1.5 1.5	2530 2395 1696	111 107 77	25.72 23.35 17.98	0.29 0.38 0.29
68.9	74.3	100	ANDESITE Light green, apohanitic same as previously Both contacts moderately serpentized	43494 43495 43496	68.9 70.9 72.9	70.9 72.9 74.3	2 2 1.4	62 30 306	23 26 31	8.43 4.73 6.89	0.05 0.01 0.02
74.3	78.6	100	SERPENTINITE Moderately listwanized; dark grey to black; talcy-carbonaceous webs throughout	43497 43498 43499	74.3 75.8 77.3	75.8 77.3 78.6	1.5 1.5 1.3	1694 1984 2181	82 92 96	22.00 24.52 23.59	0.21 0.25 0.28
78.6	80.1	100	ANDESITE Moderately sepentized; lower contact 30° to CA	43500	78.6	80.1	1.5	377	36	10.66	0.10
80.1	81.8	100	SERPENTINITE Moderately listwanized same as previously	43501	80.1	81.8	1.8	2159	101	22.24	0.80
81.8	89.1	100	ANDESITE Light green, solid intact cores ; lower contact is moderately serpentized	43502 43503 43504 43505	81.8 83.8 85.8 87.8	83.8 85.8 87.8 89.1	2 2 2 1.3	375 163 34 536	31 17 12 40	9.96 6.17 2.65 6.69	0.01 0.01 0.01 0.01
89.1	102.8	100	SERPENTINIITE Absolute black; homogeneously black;	43506 43507	89.1 90.6	90.6 92.1	1.5 1.5	2252 2122	102 105	24.43 24.84	0.30 0.25

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	Ni ppm	Co ppm	Mg %	Cr %
			Magnetic; without conspicuous listwanization	43508	92.1	93.6	1.5	2361	115	25.99	0.32
				43509	93.6	95.1	1.5	2298	110	26.84	0.24
				43510	95.1	96.6	1.5	2356	115	26.62	0.29
				43511	96.6	98.1	1.5	2358	117	26.33	0.35
				43512	98.1	99.6	1.5	2232	109	25.99	0.28
				43513	99.6	101.1	1.5	2346	113	26.30	0.54
				43514	101.1	102.8	1.7	2483	113	26.13	0.29
102.8	106.4	100	SERPENTINIE Strong, intact, but soft, contains sub-euhedral leucocratic clasts up to 5mm wide, mod-strongly magnetic,	43515	102.8	104.6	1.8	2479	124	27.66	0.27
				43516	104.6	106.4	1.8	1944	97	21.67	0.29
106.4	107.5	100	ANDESITE Light greenish-grey, strong, intact, weakly magnetic.	43517	106.4	107.5	1.1	29	31	6.84	0.01
107.5	117.8	100	SERPENTINITE Strong, intact, but soft, contains sub-euhedral leucocratic clasts up to 5mm wide, mod-strongly magnetic,	43518	107.5	109.0	1.5	2181	105	24.55	0.30
				43519	109.0	110.5	1.5	2485	117	27.11	0.30
				43520	110.5	112.0	1.5	2275	107	25.50	0.23
				43521	112.0	113.5	1.5	2314	112	27.93	0.20
				43522	113.5	115.0	1.5	2290	109	25.10	0.30
				43523	115.0	116.5	1.5	1331	89	21.21	0.15
				43524	116.5	117.8	1.3	2110	103	24.45	0.26
117.8	118.5	100	ANDESITE Light greenish-grey, strong, intact, weakly magnetic.	43525	117.8	118.5	0.7	187	25	4.18	0.02
118.5	122.8	100	SERPENTINITE Black, magnetic, contains chrisolite veinlets @ 40 ° to c.a.	43526	118.5	120.0	1.5	2210	103	24.38	0.20
				43527	120.0	121.5	1.5	2285	110	26.89	0.22
				43528	121.5	122.8	1.3	2617	123	27.73	0.29

END OF HOLE

DIAMOND DRILL HOLE RECORD

PROPERTY:

RECORD RIDGE SOUTH

DDH RRS08-2

DIP AND AZIMUTH TESTS			CORE SIZE: NQ	TOTAL DEPTH: 123.4m	DATE STARTED June 3, 2008
DEPTH	ANGLE	AZIMUTH	HOLE ANGLE: - 90°	HOLE AZIMUTH °	DATE FINISHED: June 5, 2008
123.4m	-89.5°	205.1°	SECTION:	COLLAR ELEVATION: 1456.2m	ANALYSIS BY: Assayers Canada
			GRID LOCATION: 475S/1225 W	RECOVERY:	LOGGED BY: H.K. & C.P.
			UTM (NAD 83): 5432414 N 434677 E	CLAIM: Frank Sr. 3	CORE STORED AT: Midnight camp

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM (m)	TO (m)	Length (m)	P (g/c m³)	Ni (ppm)	Co (ppm)	Mg (%)	Cr (%)
0	0	100	No Casing									
0	20.7	100	SERPENTINITE Black, homogeneous, includes some moderately listwanitized sections at random intervals, strongly magnetic, strong, solid, intact cores.	43529 43530 43531 43532 43533 43534 43535 43536 43537 43538 43539 43540 43541	0.0 1.5 3.3 4.5 6.0 7.5 9.0 10.5 12.0 13.5 15.0 16.5 18.0	1.5 3.3 4.5 6.0 7.5 9.0 10.5 12.0 13.5 15.0 16.5 18.0 20.7	1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 2.7		2539 2563 2557 2409 2469 2565 2348 2600 2293 2256 2416 2510 2106	121 124 121 114 114 123 110 92 88 84 91 96 76	27.10 26.73 27.85 26.49 27.79 28.63 27.12 28.64 25.46 25.44 25.27 26.07 22.95	0.33 0.18 0.25 0.46 0.27 0.29 0.28 0.27 0.49 0.23 0.34 0.29 0.29
20.7	21.3	100	FAULTED/SHEARED ZONE	43542	20.7	21.3	0.6		1417	61	19.30	0.27
21.3	33.1	100	SERPENTINITE Dark grey to black, includes some moderately listwanitized sections at random intervals	43543 43544 43545 43546 43547 43548 43549 43550	21.3 22.8 24.3 25.8 27.3 28.8 30.3 31.8	22.8 24.3 25.8 27.3 28.8 30.3 31.8 33.1	1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.3		2305 2507 2424 2370 1868 1979 2310 2230	76 86 86 80 70 83 91 84	23.81 26.35 26.14 26.31 22.86 21.69 24.77 23.74	0.32 0.28 0.29 0.35 0.32 0.15 0.26 0.38
33.1	36.4	100	ANDESITE Upper contact is pulverized fault-mud and 60 ° to c.a.,	43551 43552	33.1 34.8	34.8 36.4	1.7 1.6		164 979	16 52	9.14 7.34	0.03 0.08

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM (m)	TO (m)	Length (m)	P (g/c m ³)	Ni (ppm)	Co (ppm)	Mg (%)	Cr (%)
36.4	44.0	100	SERPENTINITE Dark grey to black, includes some moderately listwanitized sections at random intervals, conspicuous talcy-carbonaceous webbing throughout	43553 43554 43555 43556 43557	36.4 37.9 39.4 40.9 42.4	37.9 39.4 40.9 42.4 44.0	1.5 1.5 1.5 1.5 1.6		2034 2454 2519 2210 2067	78 95 100 87 83	21.91 26.51 27.72 24.82 21.99	0.25 0.39 0.30 0.25 0.23
44.0	50.3	100	ANDESITE	43558 43559 43560	44.0 46.0 48.0	46.0 48.0 50.3	2 2 2.3		59 157 175	32 36 36	7.03 5.47 6.28	0.03 0.08 0.08
50.3	60.9	100	SERPENTINITE Black, homogeneous, magnetic	43561 43562 43563 43564 43565 43566 43567	50.3 51.8 53.3 54.8 56.3 57.8 59.3	51.8 53.3 54.8 56.3 57.8 59.3 60.9	1.5 1.5 1.5 1.5 1.5 1.5 1.5		1319 2316 2308 2151 2243 2364 2103	64 90 90 91 112 116 105	21.07 25.77 24.48 26.50 25.91 26.99 24.02	0.21 0.31 0.43 0.32 0.34 0.65 0.39
60.9	62.8	100	SERPENTINIZED ANDESITE	43568	60.9	62.8	1.9		1226	73	9.47	0.04
62.8	64.5	100	ANDESITE Upper contact is 60 ° to c.a.,	43569	62.8	64.5	1.7		19	27	11.34	0.01
64.5		100	SERPENTINITE Black, homogeneous, magnetic	43570 43571 43572 43573 43574 43575 43576 43577 43578 43579 43580 43581 43582 43583 43584 43585 43586	64.5 66.0 67.5 69.0 70.5 72.0 73.5 75.0 76.5 78.0 79.5 81.0 82.5 84.0 85.5 87.0 88.5	66.0 67.5 69.0 70.5 72.0 73.5 75.0 76.5 78.0 79.5 81.0 82.5 84.0 85.5 87.0 88.5 90.2	1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.7		2298 2200 3223 2331 2280 2425 2170 2300 2452 2356 2263 2504 2201 2304 2334 2350 2117	111 108 153 113 114 122 113 119 116 112 107 118 101 108 105 110 103	27.15 25.14 23.53 24.97 26.19 26.53 26.10 26.58 26.38 25.55 25.94 27.96 23.99 26.64 25.04 24.65 24.91	0.34 0.36 0.54 0.29 0.42 0.36 0.33 0.48 0.35 0.38 0.28 0.29 0.37 0.34 0.39 0.26 0.25
90.2	92.5	100	ANDESITE Lower contact is 45° to c.a., light green, aphanitic, weakly magnetic, strong, intact cores.	43587	90.2	92.5	2.3		310	24	6.63	0.03
92.5	112.3	100	SERPENTINITE Black, homogeneous, magnetic, conspicuous magnetite stockworks.	43588 43589 43590 43591 43592	92.5 94.0 95.5 97.0 98.5	94.0 95.5 97.0 98.5 100.0	1.5 1.5 1.5 1.5 1.5		2188 2209 2216 2192 2210	121 108 105 105 98	23.52 24.82 25.46 24.57 25.26	0.31 0.24 0.25 0.28 0.22

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM (m)	TO (m)	Length (m)	P (g/c m ³)	Ni (ppm)	Co (ppm)	Mg (%)	Cr (%)
				43593	100.0	101.5	1.5		2236	98	26.37	0.25
				43594	101.5	103.1	1.5		2367	112	26.26	0.32
				43595	103.1	104.5	1.5		2256	111	26.59	0.24
				43596	104.5	106.0	1.5		2356	108	26.39	0.27
				43597	106.0	107.5	1.5		2324	107	25.65	0.28
				43598	107.5	109.0	1.5		2192	89	24.04	0.22
				43599	109.0	110.5	1.5		2172	91	23.74	0.25
				43600	110.5	112.3	1.8		1998	98	25.96	0.21
112.3	113.4	100	ANDESITE Both contacts are 45° to c.a., light green, aphanitic, non- to weakly magnetic, strong, intact cores.	43601	112.3	113.4	1.1		146	50	7.46	0.05
113.4	123.4	100	SERPENTINITE Black, conspicuous magnetite stockworks; moderate listwanization with calc-talcy webs.	43602	113.4	114.9	1.5		2359	116	27.11	0.34
				43603	114.9	116.4	1.5		2475	113	27.07	0.30
				43604	116.4	117.9	1.5		2567	114	27.18	0.24
				43605	117.9	119.4	1.5		2391	108	26.35	0.22
				43606	119.4	120.9	1.5		2666	113	26.94	0.26
				43607	120.9	123.4	2.5		2231	108	26.06	0.24

END OF HOLE

DIAMOND DRILL HOLE RECORD

PROPERTY:

RECORD RIDGE SOUTH

DDH RRS08-3

DIP AND AZIMUTH TESTS			CORE SIZE: NQ	TOTAL DEPTH: 153.9m	DATE STARTED June 5, 2008
DEPTH	ANGLE	AZIMUTH	HOLE ANGLE: - 90°	HOLE AZIMUTH °	DATE FINISHED: June 9, 2008
77.72m	-89.4°	113.0°	SECTION:	COLLAR ELEVATION: 1465.6	ANALYSIS BY: Assayers Canada
153.9m	-89.0°	160.7°	GRID LOCATION: 450S/ 1275W	RECOVERY:	LOGGED BY: H.K. & C.P.
			UTM (NAD 83): 5432439 N 434627 E	CLAIM: Frank Sr. 3	CORE STORED AT: Midnight camp

DEPTH (meters) FROM TO		Recovery (%)	Description	Sample No.	FROM (m)	TO (m)	Length (m)	P (g/cm ³)	Ni (g/t)	Co (g/t)	Mg (%)	Cr %
0	1.8		CASING									
1.8	10.7	60	SERPENTINITE Black, strongly magnetic, without conspicuous listwanization, 60% of cores is moderately fragmented, megascopic pyrite mineralization up to 2%.	43608 43609 43610 43611	1.8 4.6 6.9 8.4	4.6 6.9 8.4 10.7	2.8 2.3 1.5 2.3	2.72 2.72 2.72 2.7	1933 2502 2583 2375	99 118 117 108	21.36 23.80 25.88 24.95	0.26 0.39 0.37 0.33
10.7	18.4	100	SERPENTINITE Black, strongly magnetic, without conspicuous listwanization	43612 43613 43614 43615 43616	10.7 12.2 13.7 15.2 16.7	12.2 13.7 15.2 16.7 18.4	1.5 1.5 1.5 1.5 1.7	2.7 2.7 2.65 2.65 2.7	2485 2356 2593 1918 2417	116 116 126 92 111	25.29 28.31 28.53 26.63 27.08	0.35 0.33 0.33 0.26 0.45
18.4	20.2	100	ANDESITE Serpentinized Light green, aphanitic, non-magnetic, megascopically sub-euhedral feldspar phenocrysts 1-2mm in a light green matrix. Upper contact is sharp and 60° to c.a.	43617	18.4	20.2	1.8	2.7	794	83	15.26	0.12
20.2	52.35	100	SERPENTINITE Black, strongly magnetic, without conspicuous listwanization • Thick calcite vein 0-10° to c.a. from 31.5-31.8m	43618 43619 43620 43621 43622 43623 43624 43625 43626 43627 43628 43629 43630 43631 43632	20.2 21.7 23.2 24.7 26.2 27.7 29.2 30.7 32.2 33.7 35.2 36.7 38.2 39.7 41.2 42.7	21.7 23.2 24.7 26.2 27.7 29.2 30.7 32.2 33.7 35.2 36.7 38.2 39.7 41.2 42.7	1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5	2.60 2.60 2.60 2.62 2.62 2.62 2.62 2.62 2.65 2.65 2.65 2.65 2.65 2.65 2.65 2.65	2343 2363 2434 2381 2405 2408 2402 2173 2363 2031 2214 2452 2478 2371 2284	107 104 102 95 100 107 98 98 108 103 108 113 116 111 108	25.45 25.83 26.35 26.71 27.53 26.68 25.97 25.90 26.27 24.62 26.12 27.35 27.76 27.04 25.84	0.38 0.29 0.54 0.34 0.34 0.47 0.34 0.37 0.30 0.34 0.29 0.30 0.41 0.50 0.27

DEPTH (meters) FROM TO		Recovery (%)	Description	Sample No.	FROM (m)	TO (m)	Length (m)	P (g/cm ³)	Ni (g/t)	Co (g/t)	Mg (%)	Cr %
				43633	42.7	44.2	1.5	2.68	1761	92	21.11	0.27
				43634	44.2	45.7	1.5	2.68	2228	114	24.03	0.38
				43635	45.7	47.2	1.5	2.68	2315	118	25.12	0.33
				43636	47.2	48.7	1.5	2.63	2461	127	24.97	0.34
				43637	48.7	50.2	1.5	2.63	2394	136	25.73	0.48
				43638	50.2	52.35	2.15	2.63	2327	113	26.10	0.30
52.35	53.2	100	ANDESITE Light green, aphanitic, non-magnetic, megascopically sub-euhedral feldspar phenocrysts 1-2mm in a light green matrix. Upper contact is sharp and 60° to c.a.	43639	52.35	53.2	0.85	2.72	95	36	6.05	0.02
53.2	63.0	100	SERPENTINITE Black, strongly magnetic, without conspicuous listwanization	43640	53.2	54.7	1.5	2.65	2371	102	25.52	0.33
				43641	54.7	56.2	1.5	2.65	2387	102	26.94	0.22
				43642	56.2	57.7	1.5	2.65	2363	98	26.69	0.24
				43643	57.7	59.2	1.5	2.5	2306	101	26.19	0.26
				43644	59.2	60.7	1.5	2.5	2358	111	26.62	0.36
				43645	60.7	61.9	1.2	2.5	2403	114	25.43	0.25
				43646	61.9	63.0	1.1	2.5	1897	89	20.37	0.29
63.0	79.4	100	ANDESITE Light green, aphanitic, non-magnetic, megascopically sub-euhedral feldspar phenocrysts 1-2mm in a light green matrix. Upper & lower contacts are sharp and 45° to c.a.	43647	63.0	65.0	2	2.67	104	32	5.69	0.01
				43648	65.0	67.0	2	2.68	29	24	2.17	0.008
				43649	67.0	69.0	2	2.68	26	22	2.18	0.008
				43650	69.0	71.0	2	2.68	23	22	3.56	0.008
				43651	71.0	73.0	2	2.66	437	41	5.76	0.02
				43652	73.0	75.0	2	2.64	38	21	2.66	0.007
				43653	75.0	77.0	2	2.64	54	23	3.78	0.008
				43654	77.0	79.4	2.4	2.67	41	24	4.17	0.008
79.4	83.82	100	SERPENTINITE Moderately listwanized, talcy-carbonaceous veinlets and stringers form 70% of stockworks in rocks	43655	79.4	80.9	1.5	2.85	1757	84	18.73	0.24
				43656	80.9	82.4	1.5	2.85	1597	86	19.45	0.22
				43657	82.4	83.82	1.42	2.82	2029	109	19.47	0.23
83.82	84.6	100	ANDESITE Serpentinized Light green, aphanitic, non-magnetic, megascopically sub-euhedral feldspar phenocrysts 1-2mm in a light green matrix. Lower contact is sharp and 45° to c.a.	43658	83.82	84.6	0.78	2.82	251	78	11.96	0.07
84.6	95.1	100	SERPENTINITE Black, strongly magnetic, without conspicuous listwanization	43659	84.6	86.1	1.5	2.82	2120	103	23.58	0.21
				43660	86.1	87.6	1.5	2.82	2076	103	23.31	0.26
				43661	87.6	89.1	1.5	2.58	2146	108	25.00	0.28
				43662	89.1	90.6	1.5	2.58	2009	98	23.35	0.24
				43663	90.6	92.1	1.5	2.58	2119	104	24.17	0.26
				43664	92.1	93.6	1.5	2.58	2385	115	26.53	0.30
				43665	93.6	95.1	1.5	2.59	2686	126	28.90	0.32
95.1	95.85	100	CALCITE VEIN 6-8 cm, 0-10° to c.a. within the black serpentinite	43666	95.1	95.85	0.75	n/a	1395	76	23.78	0.19

DEPTH (meters) FROM TO		Recovery (%)	Description	Sample No.	FROM (m)	TO (m)	Length (m)	P (g/cm ³)	Ni (g/t)	Co (g/t)	Mg (%)	Cr %
95.85	109.0	100	SERPENTINITE Black, strongly magnetic, without conspicuous listwanization	43667	95.85	97.35	1.5	2.6	2463	116	27.83	0.44
				43668	97.35	98.85	1.5	2.6	2538	124	27.91	0.38
				43669	98.85	100.35	1.5	2.6	2410	115	27.06	0.41
				43670	100.35	101.85	1.5	2.6	2286	108	26.12	0.35
				43671	101.85	103.35	1.5	2.6	2451	115	26.90	0.41
				43672	103.35	104.85	1.5	2.6	2345	114	26.30	0.40
				43673	104.85	106.35	1.5	2.6	2513	123	27.24	0.28
				43674	106.35	107.85	1.5	2.6	2289	117	27.81	0.30
				43675	107.85	109.0	1.15	2.6	2356	120	27.88	0.39
109.0	111.5	100	ANDESITE Light green, aphanitic, non-magnetic, megascopically sub-euhedral feldspar phenocrysts 1-2mm in a light green matrix; lower 1 m section is moderately serpentinized	43676	109.0	110.2	1.2	2.76	43	24	11.94	0.001
				43677	110.2	111.5	1.3	2.76	1165	58	10.82	0.04
111.5	128.8	100	SERPENTINITE Black, strongly magnetic, with conspicuous listwanization	43678	111.5	113.0	1.5	2.71	2387	118	26.25	0.36
				43679	113.0	114.5	1.5	2.71	2326	113	26.42	0.35
				43680	114.5	116.0	1.5	2.78	2249	108	27.59	0.37
				43681	116.0	117.5	1.5	2.78	2317	111	27.79	0.34
				43682	117.5	119.0	1.5	2.78	2236	104	26.79	0.23
				43683	119.0	120.5	1.5	2.72	2075	99	27.53	0.31
				43684	120.5	122.0	1.5	2.72	2523	123	26.53	0.38
				43865	122.0	123.5	1.5	2.72	2497	117	26.88	0.31
				43686	123.5	125.0	1.5	2.72	2341	108	25.96	0.32
				43687	125.0	126.5	1.5	2.72	2301	104	25.74	0.30
				43688	126.5	128.0	1.5	2.71	2321	118	25.74	0.34
128.8	129.5	100	ANDESITE AND SERPENTINIZED ANDESITE	43689	128.0	129.5	1.5	n/a	1023	62	21.47	0.13
129.5	132.3	100	SERPENTINITE	43690	129.5	131.0	1.5	2.65	2361	112	25.02	0.32
				43691	131.0	132.3	1.3	2.65	2301	98	25.12	0.33
132.3	136.7	100	SERPENTINE Light green to green soapstone.	43692	132.3	133.8	1.5	n/a	1847	86	19.56	0.27
				43693	133.8	135.3	1.5	n/a	1893	90	19.68	0.26
				43694	135.3	136.7	1.4	n/a	1770	85	19.01	0.23
136.7	137.8	100	SERPENTINITE Black, magnetic, upper contact is 30° to c.a.	43695	136.7	137.8	1.1	2.66	2532	124	25.21	0.38
137.8	140.5	100	SERPENTINITE Light green to green soapstone, includes small section of black serpentinite from 138.3- 139.4m	43696	137.8	139.4	1.6	2.66	2369	114	25.34	0.33
				43697	139.4	140.5	1.1	2.66	1857	88	25.25	0.24
140.5	148.4	100	SERPENTINITE Black with green tinge, moderately magnetic, light green soapstone at random intervals.	43698	140.5	142.0	1.5	2.66	2021	95	24.73	0.35
				43699	142.0	143.5	1.5	2.68	1916	87	22.92	0.33
				43700	143.5	145.0	1.5	2.68	1824	82	24.56	0.24

DEPTH (meters) FROM TO		Recovery (%)	Description	Sample No.	FROM (m)	TO (m)	Length (m)	P (g/cm ³)	Ni (g/t)	Co (g/t)	Mg (%)	Cr %
				43701 43702	145.0 146.5	146.5 148.4	1.5 2.1	2.68 2.82	1831 1949	93 94	19.88 19.10	0.33 0.25
148.4	149.7	100	SERPENTINE Light green to green soapstone. Lower contact is sharp & 30° to c.a.	43703	148.4	149.7	1.3	2.82	1827	96	17.45	0.27
149.7	153.9	100	ANDESITE TO FINE-GRAINED DIORITE Light green to greenish-grey, non-magnetic, strong, hard. Somewhat brecciated andesite (including talcy-siliceous clasts 3-5mm) from 149.7-150.5m	43704 43705	149.7 151.7	151.7 153.9	1.3 2.2	2.82 2.78	892 17	52 22	6.72 1.72	0.04 0.01

END OF HOLE

DIAMOND DRILL HOLE RECORD

PROPERTY:

RECORD RIDGE SOUTH

DDH RRS08-4

DIP AND AZIMUTH TESTS			CORE SIZE: NQ	TOTAL DEPTH: 123.1m	DATE STARTED June 10, 2008
DEPTH	ANGLE	AZIMUTH	HOLE ANGLE: - 90°	HOLE AZIMUTH °	DATE FINISHED: June 12, 2008
123.1	-89.2°	309°	SECTION:	COLLAR ELEVATION: 1456.7m	ANALYSIS BY: Assayers Canada
			GRID LOCATION: 500S/ 1275W	RECOVERY:	LOGGED BY: H.K. & C.P.
			UTM (NAD 83): 5432389N 434627E	CLAIM: Frank Sr. 3	CORE STORED AT: Midnight camp

DEPTH (meters) FROM TO		Recovery (%)	Description	Sample No.	From (m)	To (m)	Length (m)	P (g/cm ³)	Ni (ppm)	Co (ppm)	Mg (%)	Cr (%)
0	1.8		Casing									
1.8	4.6	100	HIGHLY FRAGMENTED CORES Weakly serpentinitized Consists of trachyandesite/ andesite	43706	1.8	4.6	2.8	n/a	1674	76	18.72	0.19
4.6	36.0	100	SERPENTINITE Black, strong, highly magnetic, medium grained with weak listwanization containing talcy-calcareous clasts 10-20mm	43707 43708 43709 43710 43711 43712 43713 43714 43715 43716 43717 43718 43719 43720 43721 43722 43723 43724 43725 43726 43727	4.6 6.1 7.6 9.1 10.6 12.1 13.6 15.1 16.6 18.1 19.6 21.1 22.6 24.1 25.6 27.1 28.6 30.1 31.6 33.1 34.6	6.1 7.6 9.1 10.6 12.1 13.6 15.1 16.6 18.1 19.6 21.1 22.6 24.1 25.6 27.1 28.6 30.1 31.6 33.1 36.0	1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.4	2.60 2.63 2.63 2.63 2.63 2.63 2.63 2.63 2.63 2.63 2.63 2.63 2.64 2.64 2.64 2.64 2.63 2.63 2.63 2.63 2.63	2312 2267 2671 2478 2499 2432 2356 2447 2423 2549 1740 2276 2346 2592 2540 2573 2517 2568 2502 2399 2091	106 106 117 123 111 117 110 112 110 117 85 106 101 116 119 121 117 117 127 117 100	25.23 26.80 27.89 27.21 28.27 28.25 27.72 26.99 26.57 26.35 25.24 27.00 27.71 28.44 28.31 29.24 28.44 27.72 28.16 26.27 20.40	0.27 0.33 0.27 0.27 0.33 1.16 0.30 0.39 0.29 0.27 0.25 0.24 0.24 0.33 0.19 0.28 0.25 0.29 0.27 0.25 0.16
36.0	40.9	100	DIAGABBRO Medium Grained, moderately magnetic, light greenish-grey, strong, hard, contains calcite veinlets from 39.5-40.9m • Petrographic sample taken @	43728 43729 43730	36.0 37.5 39.0	37.5 39.0 40.9	1.5 1.5 1.9	2.68 2.68 2.68	90 50 49	40 46 36	4.75 4.31 5.46	0.01 0.01 0.01

DEPTH (meters) FROM TO		Recovery (%)	Description	Sample No.	From (m)	To (m)	Length (m)	P (g/cm ³)	Ni (ppm)	Co (ppm)	Mg (%)	Cr (%)
			38.5-38.68m									
40.9	96.05	100	SERPENTINITE Light greenish-grey to black, soft, dense, moderately magnetic, . • Petrographic sample taken @ 49.05 (black with magnetite Stockwork) • Petrographic sample taken @ 72.9m (listwanized)	43731	40.9	42.0	1.1	2.70	2237	85	21.78	0.47
				43732	42.0	43.5	1.5	2.70	2379	99	26.44	0.45
				43733	43.5	45.0	1.5	2.70	2635	101	29.73	0.41
				43734	45.0	46.5	1.5	2.78	2561	100	30.49	0.62
				43735	46.5	48.0	1.5	2.78	2537	102	29.65	0.73
				43736	48.0	49.5	1.5	2.78	2634	107	29.29	0.61
				43737	49.5	51.0	1.5	2.93	2557	102	28.84	0.41
				43738	51.0	52.5	1.5	2.93	2598	102	30.25	0.46
				43739	52.5	54.0	1.5	2.93	2763	107	29.76	0.37
				43740	54.0	55.5	1.5	2.88	2631	96	30.06	0.33
				43741	55.5	57.0	1.5	2.88	2803	111	30.40	0.43
				43742	57.0	58.5	1.5	2.88	2649	106	30.64	0.41
				43743	58.5	60.0	1.5	2.88	2662	105	30.54	0.34
				43744	60.0	61.5	1.5	2.88	2702	103	29.49	0.30
				43745	61.5	63.0	1.5	2.86	2657	106	30.62	0.01
				43746	63.0	64.5	1.5	2.86	2909	113	30.84	0.38
				43747	64.5	66.0	1.5	2.86	2185	90	28.44	0.51
				43748	66.0	67.5	1.5	2.81	2711	107	28.79	0.36
				43749	67.5	69.0	1.5	2.81	2576	106	29.63	0.47
				43750	69.0	70.5	1.5	2.81	2712	115	30.47	0.40
				43751	70.5	72.0	1.5	2.81	2309	108	27.90	0.34
				43752	72.0	73.5	1.5	2.83	2543	110	27.88	0.35
				43753	73.5	75.0	1.5	2.83	2697	117	29.53	0.36
				43754	75.0	76.5	1.5	2.83	2570	105	28.55	0.39
				43755	76.5	78.0	1.5	2.83	2222	79	23.58	0.39
				43756	78.0	79.5	1.5	2.65	2482	103	26.99	0.60
				43757	79.5	81.0	1.5	2.65	2423	94	26.79	0.38
				43758	81.0	82.5	1.5	2.65	2497	101	27.36	0.45
				43759	82.5	84.0	1.5	2.65	2498	94	27.19	0.34
				43760	84.0	85.5	1.5	2.65	2276	81	26.09	0.31
				43761	85.5	87.0	1.5	2.65	2240	73	26.21	0.49
				43762	87.0	88.5	1.5	2.65	2292	86	26.60	0.40
				43763	88.5	90.0	1.5	2.70	2350	88	27.07	0.28
				43764	90.0	91.5	1.5	2.70	2381	91	26.97	0.32
				43765	91.5	93.0	1.5	2.70	2429	96	26.24	0.30
				43766	93.0	94.5	1.5	2.70	2326	82	24.84	0.27
				43767	94.5	96.05	1.55	2.70	2356	88	24.52	0.25
96.05	99.90	100	SERPENTINIZED ANDESITE Weakly to non-magnetic, upper and lower contacts are sharp and 45° to c.a., megascopically porphyroblastic with euhedral	43768	96.05	98.05	2.0	2.80	1463	55	16.69	0.18
				43769	98.05	99.90	1.85	2.80	545	49	14.62	0.09

DEPTH (meters) FROM TO		Recovery (%)	Description	Sample No.	From (m)	To (m)	Length (m)	P (g/cm ³)	Ni (ppm)	Co (ppm)	Mg (%)	Cr (%)
			to sub-euhedral phenocrysts 1-2mm wide in a green, aphanitic groundmass, strong, intact cores.									
99.90	123.1	100	SERPENTINITE Homogeneously jet-black, magnetic, without conspicuous listwanization. • Petrographic sample taken @ 109.9m ****Nomenclature subject to review of petrology****	43770	99.9	101.4	1.5	2.63	2090	74	24.42	0.29
				43771	101.4	102.9	1.5	2.63	2046	66	24.36	0.21
				43772	102.9	104.4	1.5	2.63	2428	95	27.17	0.28
				43773	104.4	105.9	1.5	2.63	2451	91	26.73	0.34
				43774	105.9	107.4	1.5	2.63	2265	89	24.89	0.35
				43775	107.4	108.9	1.5	2.63	2235	93	25.48	0.31
				43776	108.9	110.4	1.5	2.63	2480	86	26.55	0.31
				43777	110.4	111.9	1.5	2.62	2266	87	27.96	0.47
				43778	111.9	113.4	1.5	2.62	2116	87	23.52	0.33
				43779	113.4	114.9	1.5	2.62	2461	98	27.46	0.34
				43780	114.9	116.4	1.5	2.62	2121	101	24.67	9.30
				43781	116.4	117.9	1.5	2.62	2467	107	27.15	0.38
				43782	117.9	119.4	1.5	2.62	2570	109	27.80	0.41
				43783	119.4	120.9	1.5	2.62	2535	111	22.05	0.45
				43784	120.9	122.4	1.5	2.63	2565	112	27.51	0.31
				43785	122.4	123.1	0.7	2.63	2521	97	27.40	0.24

END OF HOLE

DIAMOND DRILL HOLE RECORD

PROPERTY:

RECORD RIDGE SOUTH

DDH RRS08-5

DIP AND AZIMUTH TESTS			CORE SIZE: NQ	TOTAL DEPTH: 74.7 m	DATE STARTED: June 12, 2008
DEPTH	ANGLE	AZIMUTH	HOLE ANGLE: - 90°	HOLE AZIMUTH °	DATE FINISHED: June 14, 2008
74.7m	-89.8°	159°	SECTION:	COLLAR ELEVATION: 1470.5m	ANALYSIS BY: Assayers Canada
			GRID LOCATION: 1325W/475S	RECOVERY:	LOGGED BY: H.K. & C.P.
			UTM (NAD 83): 5432414N 434577 E	CLAIM: Frank Sr. 3	CORE STORED AT: Midnight camp

DEPTH (meters) FROM TO		Recovery (%)	Description	Sample No.	From (m)	To (m)	Length (m)	P (g/cm³)	Ni (ppm)	Co (ppm)	Mg (%)	Cr (%)
0	0.6	84	Casing									
0.6	22.3	100	SERPENTINITE Dominantly listwanized with talcy-calcareous stringers, blebs and veinlets. Magnetic with strongly magnetic streaks 45 ° to c.a.	43786 43787 43788 43789 43790 43791 43792 43793 43794 43795 43796 43797 43798 43799 43800	0.6 2.3 3.8 4.8 5.3 6.8 8.3 9.8 11.3 12.8 14.3 15.8 17.3 18.8 20.3 22.3	2.3 3.8 4.8 5.3 6.8 8.3 9.8 11.3 12.8 14.3 15.8 17.3 18.8 20.3 22.3	1.7 1.5 1.0 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 2.0	2.65 2.65 2.65 2.65 2.70 2.70 2.70 2.70 2.65 2.65 2.65 2.62 2.62 2.62 2.62 2.54	2534 2477 2451 2526 2268 2512 2517 2439 2466 2456 2391 2455 2236 2061 2313	115 107 106 106 95 102 96 93 100 101 97 104 94 84 92	28.48 26.49 26.73 27.17 26.17 27.90 27.63 27.17 26.88 27.00 26.56 27.37 25.38 23.63 23.97	0.27 0.30 0.40 0.49 0.37 0.30 0.21 0.31 0.42 0.42 0.45 0.47 0.32 0.29 0.31
22.3	24.3	100	MIXED ANDESITE & serpentized ANDESITE Subject to assaying (may be changed to serpentinite.	43801 43802	22.3 23.3	23.3 24.3	1.0 1.0	2.72 2.72	805 342	60 50	10.57 10.82	0.04 0.04
24.3	45.3	100	SERPENTINITE Dominantly listwanized type with talcy-calcareous stringers, blebs and veinlets. Magnetic with strongly magnetic streaks 45 ° to c.a. Black, homogeneous serpentinite at random intervals spanning 0.3 to 2m in length.	43803 43804 43805 43806 43807 43808 43809 43810 43811 43812	24.3 25.8 27.3 28.8 30.3 31.8 33.3 34.8 36.3 37.8 37.8	25.8 27.3 28.8 30.3 31.8 33.3 34.8 36.3 37.8 39.3	1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5	2.76 2.80 2.80 2.80 2.80 2.70 2.70 2.70 2.70 2.70 2.70	2178 1910 1547 1878 2021 1999 2234 2131 2188 2054	104 91 78 91 91 95 106 104 105 95	21.37 21.39 18.18 19.69 22.92 22.57 24.32 23.79 23.09 22.20	0.38 0.37 0.30 0.33 0.34 0.33 0.36 0.31 0.37 0.30

DEPTH (meters) FROM TO		Recovery (%)	Description	Sample No.	From (m)	To (m)	Length (m)	P (g/cm ³)	Ni (ppm)	Co (ppm)	Mg (%)	Cr (%)
				43813	39.3	40.8	1.5	2.70	2140	99	23.53	0.39
				43814	40.8	42.3	1.5	2.70	1986	93	21.93	0.28
				43815	42.3	43.8	1.5	2.71	2299	110	23.68	0.43
				43816	43.8	45.3	1.5	2.71	2085	96	22.98	0.32
45.3	55.6	100	ANDESITE TO FINE-GRAINED DIORITE Megascopically euhedral to sub-euhedral mafic phenocrysts (biotite or hornblende?) 0.5-1mm in a light green, aphanitic to fine-grained groundmass.	43817	45.3	47.3	2.0	2.91	432	40	5.62	0.03
				43818	47.3	49.3	2.0	2.91	21	21	1.85	0.008
				43819	49.3	51.3	2.0	2.91	26	22	2.02	0.01
				43820	51.3	53.3	2.0	2.91	25	21	2.14	0.01
				43821	53.3	55.6	2.3	2.91	28	22	2.16	0.01
55.6	59.2	100	SERPENTINITE Dark green to black variegated veinlets, streaks and hairlines of magnetite with rare chromite on megascopic observation 30° to c.a	43822	55.6	57.4	1.8	2.70	2157	104	24.03	0.38
				43823	57.4	59.2	1.8	2.70	2345	103	24.54	0.38
59.2	74.7	100	DIORITE TO DIABASO Fine to medium grained; euhedral to subhedral phenos and mafics (biotite and hornblende on megascopic inspection) 0.5 – 1 mm in light green weakly and non-magnetic groundmass.	43824	59.2	61.2	2.0	2.91	81	21	1.73	0.01
				43825	61.2	63.2	2.0	2.91	20	19	1.51	0.009
				43826	63.2	65.2	2.0	2.91	24	20	1.70	0.01
				43827	65.2	67.2	2.0	2.91	23	21	1.56	0.01
				43828	67.2	69.2	2.0	2.91	23	26	2.33	0.01
				43829	69.2	71.2	2.0	2.91	27	32	2.46	0.01
			End of Hole	43830	71.2	73.2	2.0	2.91	57	25	2.29	0.02
				43831	73.2	74.7	1.1	2.91	58	25	2.22	0.02

END OF HOLE

DIAMOND DRILL HOLE RECORD

PROPERTY:

RECORD RIDGE SOUTH

DDH RRS08-6

DIP AND AZIMUTH TESTS			CORE SIZE: NQ	TOTAL DEPTH: 93.3m	DATE STARTED June 14, 2008
DEPTH	ANGLE	AZIMUTH	HOLE ANGLE: - 90°	HOLE AZIMUTH °	DATE FINISHED: June 16, 2008
93.3	-88.6°	144°	SECTION:	COLLAR ELEVATION: 1473.6m	ANALYSIS BY: Assayers Canada
			GRID LOCATION: 425S/ 1325W	RECOVERY:	LOGGED BY: H.K. & C.P.
			UTM (NAD 83): 5432464N 434577 E	CLAIM: Frank Sr. 3	CORE STORED AT: Midnight camp

Note: Selectively assayed for Au(g/tonne), Cr(%) and Nickel sulphide(ppm)

DEPTH (meters) FROM TO		Recov er %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni ppm	Co ppm	Mg %	Cr %	Au g/tonne	Ni-NiS ppm
0	1.8		Casing											
1.8	7.5	100	SERPENTINITE Dark grey to black with listwanization, talcy-calcareous veinlets, streaks and blebs 45° to c.a., moderately fragmented with silky soapstone (dark green).	43832 43833 43834 43835	1.2 2.7 4.2 5.7	2.7 4.2 5.7 7.5	1.5 1.5 1.5 1.8	2.63 2.63 2.63 2.60	2393 1903 1665 2142	115 96 86 102	23.61 20.32 19.54 21.07	0.36 0.26 0.26 0.29	0.03	2039
7.5	54.8	100	SERPENTINITE/ PYROXYNITE TO OLIVINE WHERELITE Subject to petrographic identification. Homogeneous black without conspicuous listwanization. Magnetic throughout, however, intensity of magnetization varies throughout, veinlets and hairlines of chromite throughout, strong hard, intact cores, aphanitic to fine-grained, megascopically olivine is discerned?	43836 43837 43838 43839 43840 43841 43842 43843 43844 43845 43846 43847 43848 43849 43850 43851 43852 43853 43854 43855 43856 43857	7.5 9.0 10.5 12.0 13.5 15.0 16.5 18.0 19.5 21.0 22.5 24.0 25.5 27.0 28.5 30.0 31.5 33.0 34.5 36.0 37.5 39.0 39.0	9.0 10.5 12.0 13.5 15.0 16.5 18.0 19.5 21.0 22.5 24.0 25.5 27.0 28.5 30.0 31.5 33.0 34.5 36.0 37.5 39.0 40.5	1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5	2.81 2.81 2.81 2.78 2.78 2.78 2.78 2.78 2.78 2.78 2.81 2.81 2.81 2.81 2.86 2.86 2.86 2.86 2.78 2.78 2.78 2.79	2301 2176 2207 2151 2193 2201 2156 2304 2398 2420 2202 2231 2264 2264 2222 2352 2339 2296 2386 2279 2381 2186	111 106 110 109 103 105 103 109 114 112 103 107 107 110 108 114 118 111 114 110 114 106	24.51 23.84 23.96 25.07 23.80 24.21 23.77 24.09 23.65 23.98 24.36 25.24 24.43 25.20 25.37 25.37 26.11 24.37 25.68 24.94 25.96 24.92	0.29 0.23 0.36 0.34 0.29 0.39 0.47 0.49 0.44 0.55 0.38 0.38 0.36 0.41 0.35 0.29 0.40 0.38 0.33 0.32 0.27 0.33	0.01 0.01 0.01 0.01 0.01 0.01 0.01 0.01 0.01 0.01 0.01 0.01 0.01 0.01 0.01 0.01 0.01 0.01 0.01 0.01 0.01 0.02	1076 949 915 982

DEPTH (meters) FROM TO		Recov er %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni ppm	Co ppm	Mg %	Cr %	Au g/tonne	Ni-NiS ppm
				43858	40.5	42.0	1.5	2.65	2411	119	25.30	0.27		
				43859	42.0	43.5	1.5	2.65	2166	107	23.99	0.24		
				43860	43.5	45.0	1.5	2.65	2256	111	23.88	0.27		
				43861	45.0	46.5	1.5	2.60	2203	109	23.78	0.51	0.02	1265
				43862	46.5	48.0	1.5	2.60	2139	104	23.61	0.26		
				43863	48.0	49.5	1.5	2.60	2131	104	23.90	0.50		
				43864	49.5	51.0	1.5	2.56	2011	108	24.59	0.32		
				43865	51.0	52.5	1.5	2.56	1955	105	23.07	0.31		
				43866	52.5	53.7	1.2	2.56	2117	114	22.53	0.26	<0.01	1490
				43867	53.7	54.8	1.1	2.56	2034	111	23.18	0.13		
54.8	55.8 5	100	SERPENTINE Dark green soapstone, upper contact is 45° to c.a.	43868	54.8	55.8 5	1.05	2.63	727	58	15.75	0.15		
55.85	93.3	100	BASALTIC ANDESITE TO DIAGABBRO Aphanitic to fine-grained, Dark-grey to dark-green, megascopically moderately pyritized up to 5%, strong, compact hard, non-magnetic. - Rick pyrite streaks and veinlets up to 1cm from 59.4- 59.7m Petrographic sample @ 68.5m	43869	55.85	58.0	2.15	2.95	48	29	3.33	0.02		
				43870	58.0	60.0	2.0	2.95	63	43	2.93	0.008		
				43871	60.0	62.0	2.0	2.95	43	22	2.54	0.02		
				43872	62.0	64.0	2.0	2.95	40	25	2.90	0.01	<0.01	6
				43873	64.0	66.0	2.0	2.95	13	23	2.43	0.008		
				43874	66.0	68.0	2.0	2.95	13	24	2.58	0.008		
				43875	68.0	70.0	2.0	2.95	15	23	2.67	0.008		
				43876	70.0	72.0	2.0	2.95	411	58	4.62	0.008		
				43877	72.0	74.0	2.0	2.95	55	26	3.27	0.04		
				43878	74.0	76.0	2.0	2.95	9	25	2.44	0.01		
				43879	76.0	78.0	2.0	2.95	9	24	2.08	0.009\		
				43880	78.0	80.0	2.0	2.95	8	21	1.80	0.008		
				43881	80.0	82.0	2.0	2.95	15	21	2.08	0.008		
				43882	82.0	84.0	2.0	2.95	9	20	1.63	0.008	0.03	3
				43883	84.0	86.0	2.0	2.95	43	23	2.20	0.01		
				43884	86.0	88.0	2.0	2.95	10	30	2.19	0.005		
				43885	88.0	90.0	2.0	2.95	39	30	2.12	0.001		
				43886	90.0	92.0	2.0	2.95	62	32	2.58	0.001		
				43887	92.0	93.3	1.3	2.95	28	31	2.93	0.001		

END OF HOLE

DIAMOND DRILL HOLE RECORD

PROPERTY: RECORD RIDGE SOUTH

DDH RRS08-7

DIP AND AZIMUTH TESTS			CORE SIZE: NQ	TOTAL DEPTH: 123.4 m	DATE STARTED: June 17, 2008
DEPTH	ANGLE	AZIMUTH	HOLE ANGLE: - 90°	HOLE AZIMUTH °	DATE FINISHED: June 18, 2008
123.4	-89.2°	131°	SECTION:	COLLAR ELEVATION: 1446.7m	ANALYSIS BY: Assayers Canada
			GRID LOCATION:1175W / 450S	RECOVERY:	LOGGED BY: H.K. & C.P.
			UTM (NAD 83): 5432439 N 434727E	CLAIM: Frank Sr. 3	CORE STORED AT: Midnight camp

Note: (Check samples) Selectively assayed for Au & Nickel sulphide

[illegible]

DEPTH (meters) FROM TO		Recovery (%)	Description	Sample No.	From (m)	To (m)	Length (m)	P (g/cm ³)	Ni (%)	Co (ppm)	Mg (%)	Cr (%)	Au g/tonne	Ni- NiS ppm
13.7	27.4	100	PYROXENITE TO WEHRLITE Homogeneously black, very fine to fine grained without noticeable steatite serpentinization; essentially same as previously; upper cocontact sharp 65° to c.a.	43897	14.3	15.8	1.5	2.64	2073	113	24.48	0.27	<0.01	1112
				43898	15.8	17.3	1.5	2.64	1997	113	24.72	0.44		
				43899	17.3	18.8	1.5	2.62	2041	108	23.41	0.15		
				43900	18.8	20.3	1.5	2.62	2015	107	24.94	0.39		
				43901	20.3	21.9	1.5	2.62	2037	107	24.80	0.60		
				43902	21.9	23.3	1.5	2.62	2072	107	25.01	0.35		
27.4	32.4	100	MIXED SERPENTINITE AND PYROENITE About 60% milky white serpentinite with magnetite stockwork; about 40 % homogeneous black pyroxenite *Petrographic sample at 30.0 m	43903	23.3	24.8	1.5	2.62	2050	107	24.82	0.20	<0.01	1335
				43904	24.8	26.3	1.5	2.62	2174	112	25.71	0.38		
				43905	26.3	27.8	1.5	2.62	1828	105	23.75	0.60		
				43906	27.8	29.3	1.5	2.64	2108	115	25.71	0.36		
				43907	29.3	30.8	1.5	2.64	2349	110	25.42	0.28		
				43908	30.8	32.4	1.5	2.64	2277	109	25.06	0.25	<0.01	1325
32.4	41.45	100	PYROXENITE TO WEHRLITE Homogeneously black, very fine to fine grained without noticeable steatite serpentinization same as previously	43909	32.4	33.9	1.5	2.64	2394	113	27.06	0.32	<0.01	1087
				43910	33.9	35.4	1.5	2.68	2349	123	26.27	0.27		
				43911	35.4	36.9	1.5	2.68	2354	114	26.58	0.33		
				43912	36.9	38.4	1.5	2.68	2266	137	25.99	0.30		
				43913	38.4	39.9	1.5	2.68	2302	137	25.56	0.25		
				43914	39.9	41.45	1.55	2.68	2063	130	22.12	0.29	<0.01	1087
41.45	43.0	80	SERPENTINE Greenish grey steatite; highly pulverized and fragmented; non-magnetic; both contacts 35° to c.a.	43915	41.45	43.0	1.55	n/a	381	41	11.73	0.03		
43.0	48.8	100	PYROXENITE TO WEHRLITE Homogeneously black, very fine to fine grained without noticeable steatite serpentinization same as prrvioiously	43916	43.0	44.5	1.5	2.60	1977	104	23.30	0.27	0.02	1138
				43917	44.5	46.0	1.5	2.62	2144	102	24.24	0.24		
				43918	46.0	47.5	1.5	2.62	2070	108	25.16	0.25		
				43919	47.5	48.8	1.3	2.62	2139	107	24.81	0.22		
48.8	50.85	100	DIORITTE Fine to medium grainedc; salt and pepper texture; euhedral mafic crystals in light green Fine to medium grained groundmass; strong hard and non-magnetic	43920	48.8	50.85	2.05	2.77	63	37	3.35	0.03		
50.85	58.2	100	PYROXENITE TO WEHRLITE Homogeneously black, similar to above; lower 1 m section is listwanized	43921	50.85	52.4	1.5	2.62	2117	112	24.52	0.28	0.02	1262
				43922	52.4	53.9	1.5	2.62	2253	128	25.29	0.31		
				43923	53.9	55.4	1.5	2.64	2209	114	25.37	0.25		
				43924	55.4	56.9	1.5	2.64	2107	107	23.19	0.28		
				43925	56.9	58.2	1.3	2.64	1521	87	18.95	0.16		
58.2	59.2	100	SERPENTINE green soapstone	43926	58.2	59.2	1.0	2.85	622	57	15.53	0.06		
59.2	62.2	100	SERPENTINITE; Milky white type; with stockwork of hairlines and veinlets of magenetite; storongly magnetic	43927	59.2	60.7	1.5	2.85	1977	94	18.93	0.19	0.01	1135
				43928	60.7	62.2	1.5	2.85	1840	85	15.31	0.19		

[illegible]

DEPTH (meters) FROM TO		Recovery (%)	Description	Sampl e No.	From (m)	To (m)	Length (m)	P (g/cm ³)	Ni (%)	Co (ppm)	Mg (%)	Cr (%)	Au g/tonne	Ni- NiS ppm
				43965	116.5	118.0	1.5	2.68	2058	91	27.07	0.44		
				43966	118.0	119.5	1.5	2.68	2143	96	25.51	0.38		
				43967	119.5	121.0	1.5	2.68	2052	94	25.93	0.52		
				43968	121.0	122.5	1.5	2.68	2144	102	26.28	0.37	0.01	1136
				43969	122.5	123.4	0.9	2.68	1988	94	25.51	0.36		

END OF HOLE

DIAMOND DRILL HOLE RECORD

PROPERTY: RECORD RIDGE SOUTH

DDH RRS08-8

DIP AND AZIMUTH TESTS			CORE SIZE: NQ	TOTAL DEPTH: 123.7 m	DATE STARTED June 19, 2008
DEPTH	ANGLE	AZIMUTH	HOLE ANGLE: - 90°	HOLE AZIMUTH °	DATE FINISHED: June 2, 2008
123.7	-89.9°	140°	SECTION:	COLLAR ELEVATION: 1437.6m	ANALYSIS BY: Assayers Canada
			GRID LOCATION: 500S/ 1175W	RECOVERY:	LOGGED BY: H.K. & C.P.
			UTM (NAD 83): 5432389N 434727 E	CLAIM: Frank Sr. 3	CORE STORED AT: Midnight camp

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm³)	Ni %	Co ppm	Mg %	Cr %
0	1.5	50	Casing									
1.5	4.0	100	SERPENTINITE Milky-white type, contains stockworks of magnetite veinlets, moderately fragmented.	43970	1.5	4.0	2.5	n/a	2198	101	23.10	0.37
4.0	11.80	100	PYROXENITE Stockworks of magnetite veinlets and hairlines. Rusted and fragmented from 10.57-10.97m	43971 43972 43973 43974 43975	4.0 5.5 7.0 8.5 10.0	5.5 7.0 8.5 10.0 11.8	1.5 1.5 1.5 1.5 1.8	2.63 2.63 2.67 2.67 2.67	1648 1977 1949 1971 1815	75 91 92 89 86	24.26 25.71 23.84 24.66 21.84	0.25 0.34 0.27 0.30 0.35
11.80	12.5	100	SERPENTINIE Light green and rusted/brecciated with soapstone-coated fractures.	43976	11.80	12.50	0.7	2.66	1608	75	16.55	0.23
12.5	15.7	100	BASALTIC ANDESITE TO DIAGABBRO Fine to medium-grained, upper contact is pulverized, but looks to be around 60° to c.a., lower contact is sharp and 45° to c.a.	43977 43978	12.5 14.1	14.1 15.7	1.6 1.6	2.76 2.76	176 924	43 59	6.15 13.26	0.05 0.14
15.7	25.15	100	SERPENTINITE (dunite in origin) Stockworks of magnetite veinlets and hairlines, lower contact is sharp and 45° to c.a.	43979 43980 43981 43982 43983 43984	15.7 17.2 18.7 20.2 21.7 23.2	17.2 18.7 20.2 21.7 23.2 25.2	1.5 1.5 1.5 1.5 1.5 2	2.65 2.67 2.67 2.67 2.65 2.65	2145 2066 2135 1953 1962 1980	106 102 99 95 91 92	23.41 22.42 22.93 22.33 21.53 20.48	0.33 0.40 0.34 0.29 0.43 0.42
25.2	31.4	100	BASALTIC ANDESITE TO DIAGABBRO Fine to medium-grained, lower contact is sharp and 40° to c.a.	43985 43986 43987	25.2 27.2 29.2	27.2 29.2 31.4	2.0 2.0 2.2	2.71 2.70 2.70	701 35 34	53 32 40	5.69 2.98 4.78	0.20 0.01 0.01
31.4	43.4	100	SERPENTINITE (dunite in origin) Stockworks of magnetite veinlets and hairlines.	43988 43989 43990 43991	31.4 32.9 34.4 35.9	32.9 34.4 35.9 37.4	1.5 1.5 1.5 1.5	2.65 2.65 2.65 2.65	1563 2179 2203 2297	74 103 104 113	17.19 22.14 23.78 25.47	0.22 0.30 0.34 0.20

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni %	Co ppm	Mg %	Cr %
				43992	37.4	38.9	1.5	2.65	2206	106	23.04	0.30
				43993	38.9	40.4	1.5	2.68	2119	107	23.86	0.20
				43994	40.4	41.9	1.5	2.68	2187	107	24.26	0.22
				43995	41.9	43.4	1.5	2.68	1891	99	21.83	0.28
43.4	48.8	100	SERPENTINITE Greenish-grey to dark-grey, highly serpentinized with conspicuous soft, green steatite (soapstone), weakly to moderately magnetic, lower contact is gradational.	43996	43.4	44.9	1.5	2.71	793	68	15.40	0.09
				43997	44.9	46.4	1.5	2.71	957	68	13.89	0.11
				43998	46.4	47.9	1.5	2.71	1950	92	20.10	0.28
				43999	47.9	48.8	0.9	2.71	2039	99	21.54	0.23
48.8	53.8	100	SERPENTINITE (dunite in origin) Stockworks of magnetite veinlets and hairlines.	44000	48.8	50.3	1.5	2.72	2211	104	23.32	0.31
				44001	50.3	51.8	1.5	2.72	2433	111	24.22	0.29
				44002	51.8	53.8	2.0	2.72	2430	112	25.66	0.17
53.8	54.1	100	SERPENTINITE Dark green, green soapstone looking	44003	53.8	54.1	0.3		928	62	21.09	0.10
54.1	57.0	100	PYROXENITE Stockworks of magnetite veinlets and hairlines.; may be also called black dunite; strong intact	44004	54.1	55.6	1.5		2387	109	25.98	0.17
				44005	55.6	57.0	1.8		2301	106	25.43	0.34
57.0	57.7	100	SERPENTINE Green to dark green; non-magnetic to weakly magnetic	44006	57.0	57.7	0.7		767	56	20.70	0.06
57.7	65.3	100	SERPENTINITE (dunite in origin) Stockworks of magnetite veinlets and hairlines.; may be also called black dunite; strong intact	44007	57.7	59.0	1.3		1939	100	22.85	0.28
				44008	59.0	60.5	1.5		2199	112	23.61	0.36
				44009	60.5	62.0	1.5		1778	84	22.64	0.24
				44010	62.0	63.5	1.5		2433	114	24.91	0.53
				44011	63.5	65.3	1.8		2309	112	24.00	0.27
65.3	65.7	100	BASALTIC ANDESITE TO DIABABRO Aphanitic to fine grained; non-magnetic; Lower contact sharp 50° to c.a.; moderately serpentinized	44012	65.3	65.7	0.4		455	63	20.87	0.12
65.7	80.6	100	SERPENTINITE (dunite in origin) Stockworks of magnetite veinlets and hairlines.; may be also called black dunite; strong intact	44013	65.7	67.2	1.5		2343	109	24.42	0.34
				44014	67.2	68.7	1.5		2364	111	25.67	0.26
				44015	68.7	70.2	1.5		2403	119	27.51	0.29
				44016	70.2	71.7	1.5		2248	112	25.11	0.20
				44017	71.7	73.2	1.5		2276	120	25.52	0.19
				44018	73.2	74.7	1.5		2399	128	26.61	0.25
				44019	74.7	76.2	1.5		2434	118	26.09	0.37
				44020	76.2	77.7	1.5		2371	109	25.02	0.30
				44021	77.7	79.2	1.5		2218	101	25.56	0.28
				44022	79.2	80.6	1.4		2025	97	23.87	0.48
80.6	81.1	100	SERPENTINE Dominated by soft green soapstone	44023	80.6	81.1	0.5		1393	164	19.30	0.18

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni %	Co ppm	Mg %	Cr %
81.1	96.3	100	SERPENTINITE (dunite in origin) Stockworks of magnetite veinlets and hairlines.; may be also called black dunite; strong intact	44024	81.1	82.6	1.5		2198	107	24.45	0.42
				44025	82.6	84.1	1.5		2113	95	26.78	0.19
				44026	84.1	85.6	1.5		2094	91	27.08	0.47
				44027	85.6	87.1	1.5		2198	98	28.01	0.34
				44028	87.1	88.6	1.5		2107	96	26.90	0.27
				44029	88.6	90.1	1.5		2034	92	26.72	0.30
				44030	90.1	91.6	1.5		1926	96	26.24	0.26
				44031	91.6	93.1	1.5		1483	88	22.37	0.37
				44032	93.1	94.6	1.5		1634	79	22.71	0.34
				44033	94.6	96.3	1.7		1724	85	23.62	0.25
96.3	104.6	100	BASALTIC ANDESITE TO DIAGABBRO Aphanitic to fine grained; non-mgnetic; Including soft green soapstone in the following section: 98.17 - 98.5 101.41 - 103.16	44034	96.3	98.3	2		410	50	12.77	0.10
				44035	98.3	100.3	2		364	48	11.77	0.07
				44036	100.3	102.3	2		541	52	11.73	0.10
				44037	102.3	104.6	2.3		861	54	17.23	0.09
104.6	115.3	100	SERPENTINITE (dunite in origin) Stockworks of magnetite veinlets and hairlines.; may be also called black dunite; strong intact	44038	104.6	106.1	1.5		2035	87	23.02	0.29
				44039	106.1	107.6	1.5		1966	83	24.31	0.25
				44040	107.6	109.1	1.5		1890	81	25.76	0.25
				44041	109.1	110.6	1.5		1979	86	26.52	0.26
				44042	110.6	112.1	1.5		2143	98	27.32	0.28
				44043	112.1	113.6	1.5		2124	101	26.57	0.29
				44044	113.6	115.3	1.7		1954	89	24.24	0.33
115.3.	115.9	100	BASALTIC ANDESITE Upper contact sharp 70° to c.a.	44045	115.3	115.9	0.6		56	42	13.34	0.01
115.9	123.75	100	SERPENTINITE (dunite in origin) Stockworks of magnetite veinlets and hairlines.; may be also called black dunite; strong intact	44046	115.9	117.4	1.5		1788	81	24.49	0.25
				44047	117.4	118.9	1.5		1960	91	26.19	0.30
				44048	118.9	120.4	1.5		1977	95	26.93	0.39
				44049	120.4	121.9	1.5		2064	90	27.46	0.54
				44050	121.9	123.7	1.8		2154	97	27.75	0.40

END OF HOLE

DIAMOND DRILL HOLE RECORD

PROPERTY: RECORD RIDGE SOUTH

DDH RRS08-9

DIP AND AZIMUTH TESTS			CORE SIZE: NQ	TOTAL DEPTH: 103.9 m	DATE STARTED June 23, 2008
DEPTH	ANGLE	AZIMUTH	HOLE ANGLE: - 90°	HOLE AZIMUTH °	DATE FINISHED: June 25, 2008
103.9	-89.5°	202°	SECTION:	COLLAR ELEVATION: 1445.6	ANALYSIS BY: Assayers Canada
			GRID LOCATION: 550S/ 1275W	RECOVERY:	LOGGED BY: H.K. & C.P.
			UTM (NAD 83): 5432339 N 434627 E	CLAIM: Frank Sr. 3	CORE STORED AT: Midnight camp

* not assayed

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni %	Co ppm	Mg %	Cr %
0	1.2	0	Casing									
1.2	4.9	65	SERPENTINITE Grey to dark-grey, listwanized by stockworks of magnetite and tacy-carbonaceous veinlets and blebs along with brecciation; also contains sporadic fractures filled with soapstone, highly fragmented cores in these areas.	44051 44052	1.2 3.0	3.0 4.9	1.8 1.9	2.76 2.76	1841 1760	86 77	22.19 22.82	0.57 0.69
4.9	16.9	100	BASALTIC ANDESITE TO DIAGABBRO Aphanitic to fine-grained, light greenish-grey, non-magnetic.; serpentized fractures in the upper 5 m section	44053 44054 44055 44056 44057 44058	4.9 6.9 8.9 10.9 12.9 14.9	6.6 8.9 10.9 12.9 14.9 16.9	2.0 2.0 2.0 2.0 2.0 2.0	2.55 2.76 2.76 2.76 2.76 2.76	99 684 526 53 35 34	32 47 41 39 40 45	21.00 18.21 11.49 5.06 4.23 4.14	0.01 0.09 0.08 0.01 0.01 0.01
16.9	20.1	100	SERPENTINE Light green, soft, non-magnetic	44059 44060	16.9 18.9	18.9 20.1	2.0 1.2	2.72 2.72	1927 1021	90 56	23.92 13.49	0.01 0.21
20.1	29.45	100	SERPENTINITE (black dunite) Contains magnetite webbing and stringers, lower contact is sharp and 45° to c.a., upper contact is broken, but looks to be 50° to c.a.	44061 44062 44063 44064 44065 44066	20.1 21.6 23.1 24.6 26.1 27.45	21.6 23.1 24.6 26.1 27.45 29.45	1.5 1.5 1.5 1.5 1.35 2.0	2.62 2.62 2.62 2.62 2.62 2.62	2233 2250 2075 2086 1880 1465	84 86 88 93 85 77	25.34 25.41 24.19 23.05 16.02 14.47	0.34 0.36 0.32 0.25 0.22 0.23
29.45	35.85	100	BASALTIC ANDESITE TO DIAGABBRO Aphanitic to fine-grained, light greenish-grey, non-magnetic, both contacts are sharp and 45° to c.a.	44067 44068 44069	29.45 31.45 33.45	31.45 33.45 35.85	2.0 2.0 2.4	3.0 2.78 2.78	30 71 91	41 41 31	3.90 9.20 4.83	0.24 0.01 0.15

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni %	Co ppm	Mg %	Cr %
35.85	63.8	100	SERPENTINITE (black dunite) Contains magnetite webbing and stringers.	44070	35.85	37.4	1.5	2.85	1152	74	17.22	0.15
				44071	37.4	38.9	1.5	2.85	1095	62	19.26	0.21
				44072	38.9	40.4	1.5	2.85	1572	71	19.07	*
				44073	40.4	41.9	1.5	2.85	1998	101	20.68	*
				44074	41.9	43.4	1.5	2.85	1558	83	21.60	*
				44075	43.4	44.9	1.5	2.80	2213	106	23.60	*
				44076	44.9	46.4	1.5	2.80	2185	108	24.74	*
				44077	46.4	47.9	1.5	2.80	2250	115	24.80	*
				44078	47.9	49.4	1.5	2.62	2155	107	24.18	*
				44079	49.4	50.9	1.5	2.62	2177	110	24.55	*
				44080	50.9	52.4	1.5	2.62	2244	109	24.96	*
				44081	52.4	53.9	1.5	2.62	2208	105	23.99	*
				44082	53.9	55.4	1.5	2.68	2119	98	23.43	*
				44083	55.4	56.9	1.5	2.68	2241	109	22.12	*
				44084	56.9	58.4	1.5	2.68	2120	100	21.10	*
				44085	58.4	59.9	1.5	2.70	2461	107	24.62	*
				44086	59.9	61.4	1.5	2.70	2039	100	23.10	*
				44087	61.4	62.9	1.5	2.70	2078	126	20.58	*
				44088	62.9	63.8	0.9	2.70	2298	155	17.16	*
63.8	65.0	100	BASALTIC ANDESITE Serpentinized, non-magenic; lower contact is 35° to c.a.	44089	63.8	65.0	1.2	2.70	684	57	20.16	*
65.0	73.6	100	SERPENTINITE Green to dark-grey, moderate stockworks of magnetite and talcy-carbonaceous veinlets and blebs, moderately magnetic, strong, but can be scratched readily.	44090	65.0	67.1	2.1	2.90	1898	90	17.17	*
				44091	67.1	68.6	1.5	2.90	360	43	18.53	*
				44092	68.6	70.1	1.5	2.90	1985	102	20.68	*
				44093	70.1	71.6	1.5	2.85	2110	96	23.83	*
				44094	71.6	73.6	2.0	2.85	2012	107	20.09	*
73.6	77.6	100	BASALTIC ANDESITE TO DIAGABBRO Aphanitic to fine-grained, light greenish-grey, non-magnetic, lower contacts is sharp and 50° to c.a.	44095	73.6	75.6	2.0	2.76	64	34	8.08	
				44096	75.6	77.6	2.0	2.76	35	38	5.56	
77.6	80.5	100	SERPENTINE Green, soft soapstone, highly fragmented, non-magnetic.	44097	77.6	79.1	1.5	2.70	1071	75	18.40	0.13
				44098	79.1	80.5	1.4	2.70	1284	87	17.62	0.21
80.5	84.4	100	SERPENTINITE Green to dark-grey, moderate stockworks of magnetite and talcy-carbonaceous veinlets and blebs, moderately magnetic, strong, but can be scratched readily.	44099	80.5	82.0	1.5	2.85	742	57	13.85	0.10
				44100	82.0	83.5	1.5	2.85	1384	77	16.74	0.18
				44101	83.5	84.4	0.9	2.95	1827	82	17.16	
84.4	92.2	100	SERPENTINITE Dark grey to black; moderate stockworks of magnetite and talcy-carbonaceous veinlets and blebs, moderately magnetic, strong, but can be scratched readily; lower contact	44102	84.4	85.9	1.5	2.85	2001	95	21.75	*
				44103	85.9	87.4	1.5	2.85	2068	96	21.12	*
				44104	87.4	88.9	1.5	2.85	1534	87	19.62	*
				44105	88.9	90.4	1.5	2.85	2184	111	21.65	*
				44106	90.4	92.2	1.8	2.85	1967	102	21.27	*

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni %	Co ppm	Mg %	Cr %
92.2	94.55	100	SERPENTINE Green, soft soapstone, highly fragmented, non-magnetic.	44107 44108	92.2 93.7	93.7 94.55	1.5 0.85	2.70 2.70	1451 993	75 64	15.34 14.76	
94.55	103.9	100	BASALTIC ANDESITE TO DIAGABBRO Aphanitic to fine-grained, light greenish-grey, non-magnetic	44109 44110 44111 44112 44113	94.55 96.6 98.6 100.6 102.6	96.6 98.6 100.6 102.6 103.9	2.05 2.0 2.0 2.0 1.3	2.76 2.76 2.76 2.76 2.76	35 36 46 37 38	42 46 46 40 39	3.68 3.63 3.87 3.37 3.46	

END OF HOLE

DIAMOND DRILL HOLE RECORD

PROPERTY: RECORD RIDGE SOUTH

DDH RRS08-10

DIP AND AZIMUTH TESTS			CORE SIZE: NQ	TOTAL DEPTH: 126.8 m	DATE STARTED June 24, 2008
DEPTH	ANGLE	AZIMUTH	HOLE ANGLE: - 90°	HOLE AZIMUTH °	DATE FINISHED: June 26, 2008
126.8	-88.9°	192°	SECTION:	COLLAR ELEVATION: 1420.6m	ANALYSIS BY: Assayers Canada
			GRID LOCATION: 625S/ 1225W	RECOVERY:	LOGGED BY: H.K. & C.P.
			UTM (NAD 83): 5432264N 434677E	CLAIM: Frank Sr. 3	CORE STORED AT: Midnight camp

Note: Check sampled for chromium on only sample # 44197

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni ppm	Co ppm	Mg %	Cr %
0	0.6	98	Casing									
0.6	3.9	100	SERPENTINITE Grey to dark green with stockworks of magnetite, strongly magnetic	44114 44115	0.6 2.2	2.2 3.9	1.6 1.7	2.85 2.85	2112 2047	105 111	22.16 19.98	
3.9	32.1	100	SERPENTINITE Black to dark grey, with conspicuous stockwork of magnetite veinlets and stringers with calcite stringers as well, strongly magnetic. 9.3-9.6m faulted shear zone with rusted clay.	44116 44117 44118 44119 44120 44121 44122 44123 44124 44125 44126 44127 44128 44129 44130 44131 44132 44133 44134	3.9 5.4 6.9 8.4 9.9 11.4 12.9 14.4 15.9 17.4 18.9 20.4 21.9 23.4 24.9 26.4 27.9 29.4 30.9	5.4 6.9 8.4 9.9 11.4 12.9 14.4 15.9 17.4 18.9 20.4 21.9 23.4 24.9 26.4 27.9 29.4 32.1	1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.2	2.68 2.68 2.68 2.68 2.68 2.68 2.68 2.68 2.68 2.68 2.68 2.68 2.68 2.68 2.68 2.68 2.68 2.68 2.68	1552 2113 2248 2052 2017 1931 2144 2181 1639 2297 2236 2228 2223 2215 2319 2251 1651 2211 1948	79 103 111 102 99 99 99 100 87 105 101 102 105 98 107 102 79 110 91	21.01 23.13 24.50 22.55 22.69 23.08 22.96 24.05 20.03 22.29 22.13 22.19 22.19 22.04 23.17 21.82 19.82 23.10 20.25	
32.1	33.7	100	SERPENTININE (brecciated) Brecciated serpentinite/serpentine, soft weakly to non-magnetic, upper contact is 30° to c.a., lower contact is rusted and 30° to c.a.	44135	32.1	33.7	1.6	2.73	576	56	17.23	

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni ppm	Co ppm	Mg %	Cr %
33.7	36.4	100	SERPENTINIZED ANDESITE/ BASALTIC ANDESITE 35.6-36.4m is fresh, strong, intact basaltic andesite.	44136 44137	33.7 35.1	35.1 36.4	1.4 1.3	2.85 2.85	178 429	47 46	6.13 6.40	
36.4	37.4	100	SERPENTINE (brecciated) Brecciated serpentinite/serpentine, soft weakly to non-magnetic.	44138	36.4	37.4	1.0		614	52	15.43	
37.4	49.4	100	SERPENTINITE Dark grey to dark green with stockworks of magnetite, strongly magnetic including green serpentinite at 41.9 - 43.4	44139 44140 44141 44142 44143 44144 44145 44146	37.4 38.9 40.4 41.9 43.4 44.9 46.4 47.9	38.9 40.4 41.9 43.4 44.9 46.4 47.9 49.4	1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5	2.80 2.80 2.80 2.73 2.75 2.75 2.75 2.75	2171 1092 1843 653 1758 1789 1588 1966	104 63 89 56 90 81 79 96	18.01 18.78 17.79 17.71 19.08 20.89 20.62 20.03	
49.4	50.1	100	BASALTIC ANDESITE Aphanitic, light greenish-grey, non-magnetic, strong, intact.	44147	49.4	50.1	0.7	2.75	121	42	10.43	
50.1	52.3	100	SERPENTINITE Dark green to greenish-black, weakly magnetic.	44148	50.1	52.3	2.2	2.75	1267	71	18.18	
52.3	52.8	100	SERPENTINE Soapstone, soft, pulverized.	44149	52.3	52.8	0.5	2.83	491	53	18.16	
52.8	59.4	100	SERPENTINITE Dark green to greenish-black, thinly banded soapstone and calcite streaks 70° to c.a. at random intervals	44150 44151 44152 44153 44154	52.8 54.3 55.8 57.3 58.8	54.3 55.8 57.3 58.8 59.4	1.5 1.5 1.5 1.5 0.6	2.83 2.83 2.83 2.83 2.83	1818 1110 1161 1151 1366	87 75 69 76 89	19.18 18.40 16.25 16.36 15.82	
59.4	64.7	100	DIAGABBRO TO BASALTIC ANDESITE Light green to greenish-grey, aphanitic to fine-grained, megascopically equigranular, sub-euhedral feldspar phenocrysts, chloties are also dominant throughout. 63.5-64.7m is dominated by fragmented, pulverized soapstone.	44155 44156 44157	59.4 61.4 63.4	61.4 63.4 64.7	2.0 2.0 1.3	2.76 2.76 2.76	39 35 769	35 35 62	3.46 3.15 12.21	
64.7	71.7	100	SERPENTINITE Dark green to greenish-black, thinly banded soapstone and calcite streaks 70° to c.a. at random intervals but pronounced at lower 1 m section	44158 44159 44160 44161 44162	64.7 66.2 67.7 69.2 70.7	66.2 67.7 69.2 70.7 71.7	1.5 1.5 1.5 1.5 1	2.95 2.95 2.95 2.95 2.82	1547 1609 1862 1625 630	80 85 93 89 57	16.03 16.80 18.87 17.34 15.85	

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni ppm	Co ppm	Mg %	Cr %
71.7	77.6	100	DIAGABBRO Fine to medium-grained, upper contact is completely serpentinitized with soapstone, lower contact is sharp and 35° to c.a.	44163 44164 44165	71.7 73.75 75.75	73.75 75.75 77.6	2.05 2.0 1.85	2.76 2.76 2.76	47 45 173	35 31 36	8.48 6.44 5.96	
77.6	78.75	100	SERPENTINITE Dark green to greenish-black, thinly banded soapstone and calcite streaks 70° to c.a. at random intervals	44166	77.6	78.75	1.15	2.85	1564	77	16.51	
78.75	80.9	100	DIAGABBRO Fine to medium-grained, lower contact is completely serpentinitized with soapstone, upper contact is assumed to be 60° to c.a.	44167	78.75	80.9	2.15	2.76	188	40	6.67	
80.9	92.8	100	SERPENTINITE Black with speckled blebs of talc that are 2-3mm across, strongly magnetic.	44168 44169 44170 44171 44172 44173 44174 44175	80.9 82.4 83.9 85.4 86.9 88.4 89.9 91.4	82.4 83.9 85.4 86.9 88.4 89.9 91.4 92.8	1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.4	2.65 2.65 2.65 2.65 2.65 2.65 2.65 2.65	1997 2020 2018 1970 2334 2137 1768 1795	100 102 109 105 119 105 92 96	21.99 23.26 23.46 23.37 25.09 22.66 20.97 21.98	
92.8	93.3	100	SERPENTINITE Dark green to greenish grey, non-magnetic soapstone looking	44176	92.8	93.3	0.5	2.65	532	41	20.36	
93.3	99.9	100	SERPENTINITE Black with speckled blebs of talc that are 2-3mm across, strongly magnetic.	44177 44178 44179 44180	93.3 94.8 96.3 97.8	94.8 96.3 97.8 99.9	1.5 1.5 1.5 2.1	2.65 2.65 2.65 2.65	1995 2064 2162 1990	100 99 104 99	22.86 23.90 24.04 22.70	
99.9	117.0	100	SERPENTINITE Homogeneous black without talcy blebs, denser than previous serpentinite section, strongly magnetic.	44181 44182 44183 44184 44185 44186 44187 44188 44189 44190 44191	99.9 101.4 102.9 104.4 105.9 107.4 108.9 110.4 111.9 113.4 114.9	101.4 102.9 104.4 105.9 107.4 108.9 110.4 111.9 113.4 114.9 117.0	1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 2.1	2.89 2.89 2.89 2.89 2.89 2.89 2.89 2.89 2.89 2.89 2.89	2220 2124 2128 2338 2084 2291 1805 2365 2265 2137 2331	107 104 109 117 105 120 103 115 114 108 120	24.24 24.59 25.80 26.49 25.54 26.51 25.42 26.48 25.84 25.05 26.64	
117.0	126.8	100	SERPENTINITE Black with speckled blebs of talc that are 2-3mm across, strongly magnetic.	44192 44193 44194 44195 44196 44197	117.0 118.5 120.0 121.5 123.0 124.5	118.5 120.0 121.5 123.0 124.5 126.8	1.5 1.5 1.5 1.5 1.5 2.3	2.65 2.65 2.65 2.65 2.65 2.65	2252 2215 2165 2192 1934 2034	116 110 105 107 97 99	27.24 25.46 24.62 24.96 22.43 22.88	0.28

END OF HOLE

DIAMOND DRILL HOLE RECORD

PROPERTY: RECORD RIDGE SOUTH

DDH RRS08-11

DIP AND AZIMUTH TESTS			CORE SIZE: NQ	TOTAL DEPTH: 123.8m	DATE STARTED June 26, 2008
DEPTH	ANGLE	AZIMUTH	HOLE ANGLE: - 90°	HOLE AZIMUTH °	DATE FINISHED: July 1, 2008
123.7	-88.6°	132°	SECTION:	COLLAR ELEVATION: 1420.3m	ANALYSIS BY: Assayers Canada
			GRID LOCATION: 600S/ 1175W	RECOVERY:	LOGGED BY: H.K. & C.P.
			UTM (NAD 83): 5432289N 434727E	CLAIM: Frank Sr. 3	CORE STORED AT: Midnight camp

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni %	Co ppm	Mg %	Cr %
0	1.2		Casing									
1.2	4.9	100	SERPENTINITE Dark grey to black with moderate stockworks of magnetite veinlets and blebs; in general weakly limoto-hematized, moderately fragmented.	44198 44199	1.2 3.0	3.0 4.9	1.8 1.9	2.65 2.65	2076 2128	99 101	20.87 22.23	0.45 0.32
4.9	5.6	100	SERPENTINITE Dark green, compact hard	44200	4.9	5.6	0.7	2.76	2342	118	22.51	0.41
5.6	10.6	100	SERPENTINITE Dark grey to black with moderate stockworks of magnetite veinlets and blebs; in general weakly limoto-hematized, Mottled talcy blebs.	44201 44202 44203	5.6 7.1 8.6	7.1 8.6 10.6	1.5 1.5 2.0	2.60 2.60 2.60	1944 1826 2038	103 98 108	22.71 21.14 23.94	
10.6	18.8	100	SERPENTINITE Black with mottled talcy blebs, strongly magnetic	44204 44205 44206 44207 44208 44209	10.6 12.1 13.6 15.1 16.6 17.7	12.1 13.6 15.1 16.6 17.7 18.8	1.5 1.5 1.5 1.5 1.5 1.1	2.60 2.60 2.60 2.60 2.60 2.63	2073 2166 1918 1911 2271 2101	109 114 106 107 127 117	24.87 26.86 25.42 24.12 24.69 23.92	
18.8	25.4	100	SERPENTINITE Homogeneously black, without conspicuous magnetite stockworks and mottled with talcy blebs.	44210 44211 44212 44213	18.8 20.3 21.8 23.3	20.3 21.8 23.3 25.4	1.5 1.5 1.5 2.1	2.63 2.63 2.63 2.63	1833 1921 1867 1912	94 96 96 108	23.71 23.76 24.49 23.48	
25.4	29.7	100	BASALTIC ANDESITE TO DIAGABBRO Both contacts are sharp and 40° to c.a.	44214 44215	25.4 27.4	27.4 29.7	2.0 2.3	2.76 2.76	50 335	46 56	4.40 7.52	
29.7	104.87	100	SERPENTINITE Homogeneously black, without conspicuous magnetite stockworks and slightly mottled with talcy blebs at random intervals.	44216 44217 44218	29.7 31.2 32.7	31.2 32.7 34.2	1.5 1.5 1.5	2.65 2.65 2.65	2050 1577 2007	107 96 112	25.18 20.12 23.87	

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni %	Co ppm	Mg %	Cr %
			33.26-33.36m is a calcite vein at 20° to c.a. - Fragmented from 39.31-39.4m and 53.3-53.64m.	44219	34.2	35.7	1.5	2.65	2203	117	25.40	
				44220	35.7	37.2	1.5	2.65	2096	115	23.90	
				44221	37.2	38.7	1.5	2.65	2104	112	23.96	
				44222	38.7	40.2	1.5	2.65	2001	108	24.67	
				44223	40.2	41.7	1.5	2.65	1990	111	24.73	
				44224	41.7	43.2	1.5	2.65	1912	108	24.26	
				44225	43.2	44.7	1.5	2.65	2228	114	24.77	
				44226	44.7	46.2	1.5	2.65	2155	112	24.92	
				44227	46.2	47.7	1.5	2.65	2133	112	25.61	
				44228	47.7	49.2	1.5	2.65	1631	95	23.58	
				44229	49.2	50.7	1.5	2.65	2130	112	24.82	
				44230	50.7	52.2	1.5	2.65	2000	106	24.08	
				44231	52.2	53.7	1.5	2.65	1960	108	24.31	
				44232	53.7	55.2	1.5	2.65	2188	117	24.58	
				44233	55.2	56.7	1.5	2.65	2064	113	24.08	
				44234	56.7	58.2	1.5	2.65	2136	132	25.28	
				44235	58.2	59.7	1.5	2.65	2394	127	27.54	
				44236	59.7	61.2	1.5	2.65	2160	117	26.83	
				44237	61.2	62.7	1.5	2.65	2128	112	26.12	
				44238	62.7	64.2	1.5	2.65	2208	115	26.49	
				44239	64.2	65.7	1.5	2.65	2399	129	27.46	
				44240	65.7	67.2	1.5	2.65	2261	119	27.02	
				44241	67.2	68.7	1.5	2.65	2121	113	25.02	
				44242	68.7	70.2	1.5	2.65	2185	110	25.32	
				44243	70.2	71.7	1.5	2.65	2425	122	25.53	
				44244	71.7	73.2	1.5	2.65	2033	106	24.39	
				44245	73.2	74.7	1.5	2.65	2154	108	26.17	
				44246	74.7	76.2	1.5	2.65	2205	112	26.81	
				44247	76.2	77.7	1.5	2.65	2302	122	27.81	
				44248	77.7	79.2	1.5	2.65	2379	133	28.62	
				44249	79.2	80.7	1.5	2.65	2292	129	26.58	
				44250	80.7	82.2	1.5	2.65	2163	107	26.28	
				44251	82.2	83.7	1.5	2.65	2050	94	24.88	
				44252	83.7	85.2	1.5	2.65	2034	103	24.80	
				44253	85.2	86.7	1.5	2.65	2044	100	25.27	
				44254	86.7	88.2	1.5	2.65	2187	107	25.89	
				44255	88.2	89.7	1.5	2.65	1646	95	21.57	
				44256	89.7	91.2	1.5	2.65	2283	124	27.32	
				44257	91.2	92.7	1.5	2.65	2252	125	26.28	
				44258	92.7	94.2	1.5	2.65	2157	104	27.38	
				44259	94.2	95.7	1.5	2.65	2014	105	25.79	
				44260	95.7	97.2	1.5	2.65	2117	112	26.24	
				44261	97.2	98.7	1.5	2.65	2163	117	26.21	

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni %	Co ppm	Mg %	Cr %
				44262	98.7	100.2	1.5	2.65	2120	121	25.70	
				44263	100.2	101.7	1.5	2.65	2188	115	24.98	
				44264	101.7	103.2	1.5	2.65	1994	106	24.24	
				44265	103.2	104.87	1.67	2.65	1883	86	24.23	
104.87	105.7	100	BASALTIC ANDESITE TO DIAGABBRO	44266	104.87	105.7	0.83	2.76	54	33	4.27	
105.7	115.0	100	SERPENTINITE Homogeneously black, without conspicuous magnetite stockworks and slightly mottled with talcy blebs at random intervals.	44267	105.7	107.2	1.5	2.65	1922	125	23.79	
				44268	107.2	108.7	1.5	2.65	2352	146	26.74	
				44269	108.7	110.2	1.5	2.65	2283	194	27.82	
				44270	110.2	111.7	1.5	2.65	2260	150	26.90	
				44271	111.7	113.2	1.5	2.65	2248	131	27.77	
				44272	113.2	115.0	1.8	2.65	2130	130	26.59	
115.0	123.75	100	SERPENTINITE Homogeneously black, without conspicuous magnetite stockworks and moderately mottled with talcy blebs up to 4mm across. Much more mottling than previous section.	44273	115.0	116.5	1.5	2.62	2224	121	25.56	
				44274	116.5	118.0	1.5	2.62	2259	121	26.30	
				44275	118.0	119.5	1.5	2.60	2232	128	25.47	
				44276	119.5	121.0	1.5	2.60	2089	120	24.74	
				44277	121.0	122.5	1.5	2.60	2204	118	25.02	
				44278	122.5	123.8	1.3	2.60	1972	114	24.50	

END OF HOLE

DIAMOND DRILL HOLE RECORD

PROPERTY: RECORD RIDGE SOUTH

DDH RRS08-12

DIP AND AZIMUTH TESTS			CORE SIZE: NQ	TOTAL DEPTH: 122.2 m	DATE STARTED July 1, 2008
DEPTH	ANGLE	AZIMUTH	HOLE ANGLE: - 90°	HOLE AZIMUTH °	DATE FINISHED: July 2, 2008
122.2	-87.5°	018°	SECTION:	COLLAR ELEVATION: 1410.5m	ANALYSIS BY: Assayers Canada
			GRID LOCATION: 650S/ 1175W	RECOVERY:	LOGGED BY: H.K. & C.P.
			UTM (NAD 83): 5432239 N 434727 E	CLAIM: Frank Sr. 3	CORE STORED AT: Midnight camp

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm³)	Ni %	Co ppm	Mg %
0	1.2		Casing								
1.2	2.6	65	SERPENTINITE Magnetic, soft, moderately fragmented.	44279	1.2	2.6	1.4	2.60	2369	116	26.64
2.6	49.0	100	SERPENTINITE Black, strongly magnetic, without conspicuous talcy/calcareous blebs, lower contact shows a gradual interfingering contact trending 70° to the c.a.; contains some fractures at random intervals that are healed with rusted talcy-calcareous linings, most fractures are 35° to c.a. Frequency of fractures increases from 17.0-19.0m	44280	2.6	4.1	1.5	2.60	2191	113	25.48
				44281	4.1	5.6	1.5	2.60	2025	108	26.02
				44282	5.6	7.1	1.5	2.60	2106	109	26.08
				44283	7.1	8.6	1.5	2.60	2073	108	24.96
				44284	8.6	10.1	1.5	2.60	2286	113	26.94
				44285	10.1	11.6	1.5	2.60	2018	107	24.37
				44286	11.6	13.1	1.5	2.62	2195	114	26.24
				44287	13.1	14.6	1.5	2.62	2176	116	26.23
				44288	14.6	16.1	1.5	2.62	2374	121	27.34
				44289	16.1	17.6	1.5	2.74	2265	113	25.72
				44290	17.6	19.1	1.5	2.74	2436	121	26.78
				44291	19.1	20.6	1.5	2.74	2245	116	26.49
				44292	20.6	22.1	1.5	2.74	2366	125	27.37
				44293	22.1	23.6	1.5	2.74	2506	130	28.47
				44294	23.6	25.1	1.5	2.74	2125	112	25.47
				44295	25.1	26.6	1.5	2.74	2470	121	28.37
				44296	26.6	28.1	1.5	2.71	2288	114	26.51
				44297	28.1	29.6	1.5	2.71	2199	114	26.85
				44298	29.6	31.1	1.5	2.71	2182	116	27.78
				44299	31.1	32.6	1.5	2.71	2238	112	25.96
				44300	32.6	34.1	1.5	2.71	2256	108	26.16
				44301	34.1	35.6	1.5	2.71	2469	94	28.03
				44302	35.6	37.1	1.5	2.71	2337	81	26.34
				44303	37.1	38.6	1.5	2.71	2370	79	26.76

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni %	Co ppm	Mg %
				44304	38.6	40.1	1.5	2.74	2528	84	27.73
				44305	40.1	41.6	1.5	2.74	2389	80	27.49
				44306	41.6	43.1	1.5	2.74	2280	72	26.72
				44307	43.1	44.6	1.5	2.74	1915	61	24.59
				44308	44.6	46.1	1.5	2.56	2186	75	25.59
				44309	46.1	47.6	1.5	2.56	2121	74	25.86
				44310	47.6	49.0	1.4	2.56	1908	67	22.93
49.0	82.7	100	DIAGABBRO Medium-coarse grained, dark grey with a “salt & Pepper” appearance, hard, non- magnetic, solid, intact, hard, large (3-4mm) leucocratic phenocrysts as well as smaller (1- 2mm) hornblende phenocrysts (six-sided with 60°/120° cleavage), contains sporadic talcy- calcareous lines fractures at random intervals.	44311	49.0	51.0	2.0	2.86	330	38	8.4
				44312	51.0	53.0	2.0	2.86	346	39	8.25
				44313	53.0	55.0	2.0	2.86	347	38	8.20
				44314	55.0	57.0	2.0	2.86	351	38	8.57
				44315	57.0	59.0	2.0	2.86	351	38	8.81
				44316	59.0	61.0	2.0	2.86	349	38	8.61
				44317	61.0	63.0	2.0	2.86	344	38	8.56
				44318	63.0	65.0	2.0	2.86	332	37	8.11
				44319	65.0	67.0	2.0	2.86	346	42	9.56
				44320	67.0	69.0	2.0	2.86	327	38	8.29
				44321	69.0	71.0	2.0	2.86	314	36	7.88
				44322	71.0	73.0	2.0	2.86	307	37	7.72
				44323	73.0	75.0	2.0	2.86	316	38	7.72
				44324	75.0	77.0	2.0	2.86	337	36	7.83
				44325	77.0	79.0	2.0	2.86	384	41	9.22
				44326	79.0	81.0	2.0	2.86	352	39	8.81
				44327	81.0	82.7	1.7	2.86	345	39	8.69
82.7	94.7	100	SERPENTINITE Black, strongly magnetic, without conspicuous talcy/calcareous blebs.	44328	82.7	84.2	1.5	2.80	2280	107	28.20
				44329	84.2	85.7	1.5	2.80	2052	96	26.33
				44330	85.7	87.2	1.5	2.80	2385	121	30.06
				44331	87.2	88.7	1.5	2.80	2496	138	30.87
				44332	88.7	90.2	1.5	2.80	2316	118	29.87
				44333	90.2	91.7	1.5	2.80	2234	118	28.77
				44334	91.7	93.2	1.5	2.80	2340	132	27.98
				44335	93.2	94.7	1.5	2.80	1969	112	27.05
94.7	97.3	100	DIAGABBRO Medium-coarse grained, dark grey with a “salt & Pepper” appearance, hard, non- magnetic, solid, intact, hard, large (3-4mm) leucocratic phenocrysts as well as smaller (1- 2mm) hornblende phenocrysts (six-sided with 60°/120° cleavage), contains sporadic talcy- calcareous lines fractures at random intervals, upper and lower contacts are sharp and 40°to c.a.	44336	94.7	96.0	1.3	2.86	540	43	10.70
				44337	96.0	97.3	1.3	2.86	479	43	11.25
97.3	107.8	100	SERPENTINITE Black, intact, magnetic, readily scratched, contains talcy blebs up to 4mm across.	44338	97.3	98.8	1.5	2.86	2528	138	27.46
				44339	98.8	100.3	1.5	2.86	2367	109	28.78
				44340	100.3	101.8	1.5	2.86	2410	88	28.16

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni %	Co ppm	Mg %
				44341	101.8	103.3	1.5	2.89	2454	90	29.26
				44342	103.3	104.8	1.5	2.89	2430	81	29.61
				44343	104.8	106.3	1.5	2.89	2418	90	29.81
				44344	106.3	107.8	1.5	2.90	2432	98	30.21
107.8	112.54	100	SERPENTINITE Black, strongly magnetic, without conspicuous talcy/calcareous blebs.	44345	107.8	109.3	1.5	2.92	2575	117	30.01
				44346	109.3	110.8	1.5	2.92	2653	123	30.00
				44347	110.8	112.54	1.74	2.92	2602	116	29.80
112.54	114.15	100	DIAGABBRO Medium-coarse grained, dark grey with a “salt & Pepper” appearance, hard, non- magnetic, solid, intact, hard, large (3-4mm) leucocratic phenocrysts as well as smaller (1- 2mm) hornblende phenocrysts (six-sided with 60°/120° cleavage), contains sporadic talcy- calcareous lines fractures at random intervals, upper contact is sharp and 30° to c.a., lower contact is somewhat fragmented.	44348	112.54	114.15	1.61	2.76	447	40	10.06
114.15	116.4	100	SERPENTINITE Black, magnetic, somewhat fragmented, numerous fracture sets (>4) coated with white talcy-calcareous linings (fizzes readily with HCl)	44349	114.15	116.4	1.25	2.65	1874	64	25.66
116.4	122.22	100	SERPENTINITE Black, strongly magnetic, without conspicuous talcy/calcareous blebs.	44350	116.4	118.2	1.8	2.85	2455	92	27.55
				44351	118.2	119.7	1.5	2.85	2627	91	28.68
				44352	119.7	121.2	1.5	2.85	2724	84	27.85
				44353	121.2	122.2	1.0	2.85	2880	85	29.06

END OF HOLE

DIAMOND DRILL HOLE RECORD

PROPERTY: RECORD RIDGE SOUTH

DDH RRS08-13

DIP AND AZIMUTH TESTS			CORE SIZE: NQ	TOTAL DEPTH: 122.8 m	DATE STARTED July 3, 2008
DEPTH	ANGLE	AZIMUTH	HOLE ANGLE: - 90°	HOLE AZIMUTH °	DATE FINISHED: July 8, 2008
123.7	-89.1°	246°	SECTION:	COLLAR ELEVATION: 1405.1m	ANALYSIS BY: Assayers Canada
			GRID LOCATION: 625S/ 1125W	RECOVERY:	LOGGED BY: H.K. & C.P.
			UTM (NAD 83): 5432264N 434777 E	CLAIM: Frank Sr. 3	CORE STORED AT: Midnight camp

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm³)	Ni %	Co ppm	Mg %
0	1.2	85	Casing								
1.2	3.45	100	SERPENTINITE Black, strongly magnetic, fragmented, rusted throughout, talcy-calcareous lining on all fractured planes	44354	1.2	3.45	2.25	2.58	2178	117	25.03
3.45	9.40	100	SERPENTINITE Dark greenish-grey, magnetic, filled with fractures that are lined with talcy-calcareous linings as well as thick (1cm) soapstone bands, somewhat fragmented due to the high frequency of fractures.	44355 44356 44357 44358	3.45 5.0 6.5 8.0	5.0 6.5 8.0 9.4	1.55 1.5 1.5 1.4	2.6 2.6 2.6 2.6	2283 1900 2096 2151	109 99 92 71	24.79 24.34 24.69 25.08
9.40	16.80	100	SERPENTINITE Black with mafic phenocrysts (pyroxene?) roughly ½ to 1mm across, magnetic, contains some mineralization (pyrite), also contains bands of rusted/ milky serpentinite that run roughly perpendicular to the c.a.	44359 44360 44361 44362 44363	9.4 10.9 12.4 13.9 15.4	10.9 12.4 13.9 15.4 16.8	1.5 1.5 1.5 1.5 1.4	2.6 2.6 2.6 2.6 2.6	2524 2448 2450 2366 2432	64 60 58 56 60	27.04 27.82 27.21 26.23 25.95
16.80	22.80	100	SERPENTINITE Dark grey with milky-white appearance, magnetic, contains phenocrysts of mafic composition roughly 1mm long, somewhat rusted throughout, frequent fracture sets running through, which are healed with talcy-calcareous linings and run at 30° or 80° to c.a.	44364 44365 44366 44367	16.8 18.3 19.8 21.3	18.3 19.8 21.3 22.8	1.5 1.5 1.5 1.5	2.58 2.58 2.58 2.63	2297 2316 2427 2279	56 57 67 72	25.33 25.01 26.36 25.40
22.80	27.30	100	SERPENTINITE Dark greenish-grey, magnetic, highly fractured throughout, gets lighter in color with white talcy blebs from 25-26.4m	44368 44369 44370	22.8 24.3 25.8	24.3 25.8 27.3	1.5 1.5 1.5	2.63 2.63 2.63	2120 1066 1285	64 49 53	25.21 22.27 27.15
27.30	46.65	100	SERPENTINITE Black, magnetic, solid, intact, contains some sporadic calcareous fractures at random intervals, lower contact is soapstone-lined,	44371 44372 44373 44374	27.3 28.8 30.3 31.8	28.8 30.3 31.8 33.3	1.5 1.5 1.5 1.5	2.63 2.63 2.63 2.63	1991 2312 2064 2151	62 70 75 76	25.80 25.66 25.88 26.51

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni %	Co ppm	Mg %
			sharp and 40° to c.a. Thick calcite vein from 35.1-35.36m	44375	33.3	34.8	1.5	2.63	2216	74	26.62
				44376	34.8	36.3	1.5	2.63	2084	82	25.33
				44377	36.3	37.8	1.5	2.63	1989	80	25.54
				44378	37.8	39.3	1.5	2.63	2344	68	27.76
				44379	39.3	40.8	1.5	2.63	2280	68	27.03
				44380	40.8	42.3	1.5	2.63	2134	77	26.47
				44381	42.3	43.8	1.5	2.63	2223	89	27.23
				44382	43.8	45.3	1.5	2.63	2158	84	25.95
				44383	45.3	46.65	1.35	2.63	1949	81	24.49
46.65	48.6	100	ANDESITE with soapstone Grey, hard, intact, non-magnetic, upper contact is pulverized and coated in soapstone, lower contact is sharp and 50° to c.a.	44384	46.65	48.6	1.95	2.77	46	4	13.87
48.6	63.2	100	SERPEENTINITE Jet black, magnetic, talc-filled fractures are common and typically run 30° or 70° to c.a.	44385	48.6	50.1	1.5	2.6	2240	85	25.14
				44386	50.1	51.6	1.5	2.6	1867	70	26.84
				44387	51.6	53.1	1.5	2.6	2022	62	26.09
				44388	53.1	54.6	1.5	2.6	2068	78	26.96
				44389	54.6	56.1	1.5	2.6	2218	82	27.98
				44390	56.1	57.6	1.5	2.6	2170	80	27.40
				44391	57.6	59.1	1.5	2.6	2246	81	26.89
				44392	59.1	60.6	1.5	2.6	2237	84	26.67
				44393	60.6	62.1	1.5	2.6	2055	84	27.13
				44394	62.1	63.2	1.1	2.6	1891	71	26.07
63.2	69.8	100	SERPENTINITE Jet-black, magnetic, contains talcy veinlets throughout section that are roughly ¼ mm across and run 45° to c.a., give rock a “cat-scratched” appearance. Pulverized from 62.55-62.69m & 68.98-69.44m	44395	63.2	64.7	1.5	2.58	2148	81	26.91
				44396	64.7	66.2	1.5	2.58	2135	82	26.76
				44397	66.2	67.7	1.5	2.58	2210	93	27.86
				44398	67.7	69.8	2.1	2.58	1828	76	26.73
69.8	75.15	100	SERPENTINITE Black, magnetic, with white talcy blebs, somewhat fragmented. Highly fragmented/pulverized from 73.3-73.45m	44399	69.8	71.3	1.5	2.62	2148	85	25.71
				44400	71.3	72.8	1.5	2.62	2164	101	25.27
				44401	72.8	74.3	1.5	2.62	2070	102	23.42
				44402	74.3	75.15	0.85	2.62	2209	97	22.50
75.15	86.4	80	BASALTIC ANDESITE/ DIAGABBRO Weakly serpentized Greenish-grey, aphanitic to fine-grained, contains felspar phenocrysts (1-2mm), hard, non-magnetic, covered in talcy-calcareous veinlets, fractures and blebs. Upper contact is 45° to c.a., section goes in and out of pulverized sections. Completely pulverized from 82.3-83.3m & 84.12-85.4m.	44403	75.15	77.15	2.0	2.76	714	48	13.24
				44404	77.15	79.15	2.0	2.76	31	28	3.84
				44405	79.15	81.15	2.0	2.76	640	42	12.62
				44406	81.15	83.3	2.15	2.76	531	35	18.16
				44407	83.3	86.4	3.1	2.76	932	51	13.46

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni %	Co ppm	Mg %
86.4	90.4	100	SERPENTINITE Jet-black, magnetic, contains some megascopic sulphides. • 88.8-89.92m is fragmented and fractured with green soft serpenitne	44408	86.4	87.9	1.5	2.60	1726	79	24.04
				44409	87.9	89.4	1.5	2.60	1417	63	24.87
				44410	89.4	90.4	1.0	2.60	452	24	21.74
90.4	94.4	100	SERPENTINITE Black, magnetic, with white talcy blebs, fragmented, contains sulphide mineralization.	44411	90.4	91.9	1.5	2.65	1007	49	22.72
				44412	91.9	93.4	1.5	2.65	1842	74	24.35
				44413	93.4	94.4	1.0	2.65	1947	84	25.62
94.4	98.0	100	SERPENTINIZED ANDESITE Grey, magnetic, hard, fragmented, aphanitic.	44414	94.4	95.9	1.5	2.73	1311	86	12.7
				44415	95.9	98.0	2.1	2.73	754	54	15.0
98.0	104.44	100	SERPENTINITE Black, magnetic, with white talcy blebs, somewhat fragmented, contains sulphide mineralization.	44416	98.0	99.5	1.5	2.65	2084	90	24.93
				44417	99.5	101.0	1.5	2.65	1982	68	25.21
				44418	101.0	102.5	1.5	2.65	2200	87	26.71
				44419	102.5	104.44	1.94	2.65	1885	75	22.31
104.44	106.7	100	SERPENTINIZED ANDESITE Grey, magnetic, hard, fragmented, aphanitic. Covered in talcy coating.	44420	104.44	106.7	2.26	2.73	1456	74	18.32
106.7	110.3	100	SERPENTINITE Black, magnetic, with white talcy blebs, somewhat fragmented, contains sulphide mineralization.	44421	106.7	108.2	1.5	2.65	2063	72	24.71
				44422	108.2	110.3	2.1	2.65	2064	108	21.39
110.3	122.83	100	ANDESITE Grey, hard, intact, weakly to non-magnetic, talc/calcareous healed fractures at random intervals and random orientations, mineralization occurs throughout (pyrite)	44423	110.3	112.3	2.0	3.0	213	42	8.52
				44424	112.3	114.3	2.0	3.0	32	39	3.29
				44425	114.3	116.3	2.0	3.0	24	37	3.00
				44426	116.3	118.3	2.0	3.0	28	40	3.35
				44427	118.3	120.3	2.0	3.0	46	40	4.07
				44428	120.3	122.8	2.5	2.9	26	31	2.66

END OF HOLE

DIAMOND DRILL HOLE RECORD

PROPERTY: RECORD RIDGE SOUTH

DDH RRS08-14

DIP AND AZIMUTH TESTS			CORE SIZE: NQ	TOTAL DEPTH: 123.75m	DATE STARTED July 8th, 2008
DEPTH	ANGLE	AZIMUTH	HOLE ANGLE: - 90°	HOLE AZIMUTH °	DATE FINISHED: June 9th, 2008
123.7	-89.6°	028°	SECTION:	COLLAR ELEVATION: 1420.3m	ANALYSIS BY: Assayers Canada
			GRID LOCATION: 525S/ 1125W	RECOVERY:	LOGGED BY: H.K. & C.P.
			UTM (NAD 83): 5432364 N 434777E	CLAIM: Frank Sr. 3	CORE STORED AT: Midnight camp

Selectively assayed for chromium : Samples 44481 -44490

DEPTH FROM	(meters) TO	Recovery %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni %	Co ppm	Mg %	Cr %
0	0.6		CASING									
0.6	11.57	100	SERPENTINITE Black, dominantly mottled by magnetite/chromite blebs and stringers, strongly magnetic, aphanitic to fine-grained.	44429 44430 44431 44432 44433 44434 44435	0.6 2.1 3.6 5.1 6.6 8.1 9.6	2.1 3.6 5.1 6.6 8.1 9.6 11.57	1.5 1.5 1.5 1.5 1.5 1.5 1.97	2.57 2.57 2.57 2.58 2.58 2.58 2.58	2054 1653 1621 2144 2102 2077 2025	86 76 74 81 110 107 108	25.95 23.60 26.09 25.53 24.83 24.75 25.15	
11.57	14.30	100	SERPENTINITE Milky-white with magnetite stockworks, moderately magnetic, upper contact is 45° to c.a., lower contact is gradational and assumed to be 45° to c.a.	44436 44437	11.57 13.07	13.07 14.30	1.5 1.23	2.58 2.58	2105 2189	112 117	24.45 25.67	
14.30	22.66	100	SERPENTINITE Black, dominantly mottled by magnetite/chromite blebs and stringers, strongly magnetic, aphanitic to fine-grained.	44438 44439 44440 44441 44442	14.3 15.8 17.3 18.8 20.3	15.8 17.3 18.8 20.3 22.66	1.5 1.5 1.5 1.5 2.36	2.58 2.58 2.58 2.58 2.58	2187 2019 2311 2137 2106	117 111 123 112 111	25.17 25.02 27.30 25.03 25.63	
22.66	26.0	100	SERPENTINITE Milky-white with magnetite stockworks, moderately magnetic,	44443 44444	22.66 24.16	24.16 26.0	1.5 1.84	2.58 2.58	2063 1996	116 112	25.33 23.50	
26.0	47.1	100	SERPENTINITE Black, dominantly mottled by magnetite/chromite blebs and stringers, strongly magnetic, aphanitic to fine-grained.	44445 44446 44447 44448 44449 44450 44451 44452 44453 44454	26.0 27.5 29.0 30.5 32.0 33.5 35.0 36.5 38.0 39.5	27.5 29.0 30.5 32.0 33.5 35.0 36.5 38.0 39.5 41.0	1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5	2.58 2.58 2.58 2.58 2.6 2.6 2.6 2.6 2.6 2.6	2123 2129 2337 2360 2158 2030 2119 2137 1886 2242	114 116 123 116 114 110 113 114 101 121	25.16 26.52 27.02 25.15 25.04 25.55 25.67 25.63 24.99 26.11	

DEPTH FROM	(meters) TO	Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni %	Co ppm	Mg %	Cr %
				44455	41.0	42.5	1.5	2.6	1985	110	24.94	
				44456	42.5	44.0	1.5	2.58	2319	122	25.90	
				44457	44.0	45.5	1.5	2.58	2108	81	26.09	
				44458	45.5	47.1	1.6	2.58	2286	80	26.03	
47.1	48.65	100	BASALTIC ANDESITE/ DIAGABBRO Aphanitic to fine-grained, megascopically porphyroblastic.	44459	47.1	48.65	1.55	2.68	546	58	7.65	
48.65	94.3	100	SERPENTINITE Black, dominantly mottled by magnetite/chromite blebs and stringers, strongly magnetic, aphanitic to fine-grained.	44460	48.65	50.15	1.5	2.58	1901	67	22.65	
				44461	50.15	57.7	1.55	2.58	2222	79	27.60	
				44462	57.7	53.2	1.5	2.58	2170	86	26.19	
				44463	53.2	54.7	1.5	2.58	2238	89	28.14	
				44464	54.7	56.2	1.5	2.58	2229	87	28.16	
				44465	56.2	57.7	1.5	2.58	2061	82	26.35	
				44466	57.7	59.2	1.5	2.58	2095	82	26.02	
				44467	59.2	60.7	1.5	2.58	1751	67	22.17	
				44468	60.7	62.2	1.5	2.58	2216	90	27.07	
				44469	62.2	63.7	1.5	2.58	1877	75	26.45	
				44470	63.7	65.2	1.5	2.58	1859	72	26.29	
				44471	65.2	66.7	1.5	2.58	2242	84	27.44	
				44472	66.7	68.2	1.5	2.58	2145	82	26.86	
				44473	68.2	69.7	1.5	2.58	2203	90	27.82	
				44474	69.7	71.2	1.5	2.58	2198	86	28.16	
				44475	71.2	72.7	1.5	2.58	2156	82	27.13	
				44476	72.7	74.2	1.5	2.58	2256	86	27.55	
				44477	74.2	75.7	1.5	2.58	2204	85	27.66	
				44478	75.7	77.2	1.5	2.58	2263	84	27.82	
				44479	77.2	78.7	1.5	2.58	2237	83	26.60	
				44480	78.7	80.2	1.5	2.58	2258	87	26.35	
				44481	80.2	81.7	1.5	2.58	2013	72	26.50	
				44482	81.7	83.2	1.5	2.58	2283	91	27.78	0.41
				44483	83.2	84.7	1.5	2.58	2229	86	25.07	0.46
				44484	84.7	86.2	1.5	2.58	2216	73	24.54	0.45
				44485	86.2	87.7	1.5	2.58	2087	68	24.40	0.37
				44486	87.7	89.2	1.5	2.58	1466	51	23.22	0.30
				44487	89.2	90.7	1.5	2.58	1852	55	21.96	0.27
				44488	90.7	92.2	1.5	2.58	1928	58	25.13	0.35
				44489	92.2	93.7	1.5	2.58	1738	52	25.30	0.32
94.3	98.2	100	SERPENTINITE Light greenish-grey, about 60% of the rock is highly fragmented with fractures that are coated with soft green soapstone	44490	93.7	95.2	1.5	2.76	1198	35	20.29	0.27
				44491	95.2	96.7	1.5	2.76	1550	53	16.78	0.22
				44492	96.7	98.2	1.5	2.76	958	34	15.13	0.10
98.2	102.8	100	BASALTIC ANDESITE Moderately serpentinized, lower contact is gouged.	44493	98.2	100.0	1.8	2.76	274	21	9.56	0.02
				44494	100.0	101.4	1.4	2.76	72	25	7.10	
				44495	101.4	102.8	1.4	2.76	219	28	6.59	

DEPTH FROM	(meters) TO	Recovery %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni %	Co ppm	Mg %	Cr %
102.8	106.05	100	SERPENTINITE Black, dense, aphanitic to fine-grained without listwanization, magnetic, lower contact is sharp and 50° to c.a.	44496 44497	102.8 104.3	104.3 106.05	1.5 1.75	2.76 2.76	1894 1453	71 58	22.13 19.07	0.42 0.28
106.05	113.6	100	BASALTIC ANDESITE/ DIAGABBRO Contains serpentinized fractures at random intervals, upper contact is sharp and 50° to c.a.	44498 44499 44500 44501 44502	106.05 107.3 108.05 110.0 112.0	107.3 108.05 110.0 112.0 113.6	1.25 0.75 1.95 2.00 1.6	2.76 2.76 2.76 2.76 2.76	167 45 50 77 303	23 14 30 23 33	12.16 11.74 3.76 3.37 3.28	0.02 0.01
113.6	119.7	100	SERPENTINITE Black, dense, aphanitic to fine-grained without listwanization, magnetic, lower contact is sharp and 45° to c.a.	44503 44504 44505 44506	113.6 115.1 116.6 118.1	115.1 116.6 118.1 119.7	1.5 1.5 1.5 1.6	2.65 2.65 2.65 2.65	2107 2136 2311 2256	97 99 110 107	19.61 20.53 22.35 22.71	
119.7	123.75	100	BASALTIC ANDESITE/ DIAGABBRO Contains serpentinized fractures at random intervals.	44507 44508	119.7 121.7	121.7 123.75	2.0 2.05	2.76 2.76	386 175	52 28	7.66 5.50	

END OF HOLE

DIAMOND DRILL HOLE RECORD

PROPERTY: RECORD RIDGE SOUTH

DDH RRS08-15

DIP AND AZIMUTH TESTS			CORE SIZE: NQ	TOTAL DEPTH: 120.7 m	DATE STARTED July 9, 2008
DEPTH	ANGLE	AZIMUTH	HOLE ANGLE: - 90°	HOLE AZIMUTH °	DATE FINISHED: July 11, 2008
120.7	-88.6°	281°	SECTION:	COLLAR ELEVATION: 1426.8m	ANALYSIS BY: Assayers Canada
			GRID LOCATION: 550S/ 1175W	RECOVERY:	LOGGED BY: H.K. & C.P.
			UTM (NAD 83): 5432339 N 434727 E	CLAIM: Frank Sr. 3	CORE STORED AT: Midnight camp

DEPTH (meters) FROM TO		Recovery %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm³)	Ni %	Co ppm	Mg %
0	0.6	80	CASING								
0.6	7.47	100	MIXED SERPENTINIZED BASALTIC ANDESITE AND ANDESITE Highly fragmented, fractures are limono-hematized, overall weakly to non-magnetic. 0.6-2.1m serpentized andesite. 2.1-3.6m Fragmented andesite to diagabbro, non-magnetic. 3.6-5.3m Diorite, med.-grained, fragmented 5.3-6.3m Basaltic andesite, weakly magnetic and serpentized. 6.3-7.47m strongly serpentized andesite, non-magnetic	44509 44510 44511 44512 44513	0.6 2.1 3.6 5.3 6.3	2.1 3.6 5.3 6.3 7.47	1.5 1.5 1.7 1.0 1.17	2.7 2.7 2.7 2.7 2.7	1834 828 272 1309 1989	96 60 48 70 110	17.15 14.72 6.68 15.79 20.69
7.47	12.0	100	SERPENTINITE Dark grey to black, visible stockworks of magnetite stringers and blebs and calc-talcy stringers.	44514 44515 44516	7.47 9.0 10.5	9.0 10.5 12.0	1.5 1.5 1.5	2.81 2.81 2.81	2243 2136 2519	105 102 113	21.04 20.83 25.01
12.0	15.9	100	SERPENTINITE Homogeneously black and dense with some listwanization at random intervals.	44517 44518 44519	12.0 13.5 14.7	13.5 14.7 15.9	1.53 1.2 1.2	2.63 2.63 2.63	2574 2271 2380	118 108 110	25.00 24.78 25.17
15.9	35.8	100	SERPENTINITE Dark grey to black, visible stockworks of magnetite stringers and blebs and calc-talcy stringers. 24.9 – 27.9 : mixed with talcy serpentine	44520 44521 44522 44523 44524 44525 44526 44527 44528	15.9 17.4 18.9 20.4 21.9 23.4 24.9 26.4 27.9	17.4 18.9 20.4 21.9 23.4 24.9 26.4 27.9 29.4	1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5	2.63 2.63 2.63 2.63 2.63 2.63 2.68 2.67 2.63	2185 2307 2303 2395 2280 2258 333 1567 2096	106 109 110 113 113 110 1 80 101	24.81 24.73 24.92 25.29 23.74 26.64 23.29 22.38 22.83

DEPTH (meters) FROM TO		Recovery %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni %	Co ppm	Mg %
				44529	29.4	30.9	1.5	2.63	2185	108	23.15
				44530	30.9	32.4	1.5	2.63	1956	99	21.26
				44531	32.4	33.9	1.5	2.63	1941	88	21.24
				44532	33.9	35.8	1.9	2.63	2227	102	22.22
35.8	45.2	100	SERPENTINITE Homogeneously black and dense with some listwanization at random intervals.	44533	35.8	37.3	1.5	2.63	2259	109	23.71
				44534	37.3	38.8	1.5	2.63	2362	114	24.40
				44535	38.8	40.3	1.5	2.63	2302	117	24.79
				44536	40.3	41.8	1.5	2.63	2275	115	24.03
				44537	41.8	43.3	1.5	2.63	2215	108	22.62
				44538	43.3	45.2	1.5	2.63	2259	113	23.61
45.2	47.55	100	SERPENTINITE Moderately listwanized with magnetite blebs.	44539	45.2	46.7	1.5	2.63	2239	112	23.73
				44540	46.7	47.55	0.85	2.63	2186	109	23.76
47.55	53.7	100	SERPENTINITE Homogeneously black and dense with some listwanization at random intervals.	44541	47.55	49.05	1.5	2.63	2576	127	24.80
				44542	49.05	50.55	1.5	2.63	2392	118	24.96
				44543	50.55	52.05	1.5	2.63	2491	118	25.57
				44544	52.05	53.7	1.65	2.63	2679	124	26.41
53.7	71.23	100	SERPENTINITE Dark grey to black, visible stockworks of magnetite stringers and blebs and calc-talcy stringers.	44545	53.7	55.2	1.5	2.71	2359	115	23.69
				44546	55.2	56.7	1.5	2.71	2475	102	23.60
				44547	56.7	58.2	1.5	2.71	2020	97	21.05
				44548	58.2	59.7	1.5	2.71	2237	115	24.32
				44549	59.7	61.2	1.5	2.71	2265	104	24.38
				44550	61.2	62.7	1.5	2.71	2382	104	23.96
				44551	62.7	64.2	1.5	2.71	2516	116	24.70
				44552	64.2	65.7	1.5	2.71	1977	105	22.24
				44553	65.7	67.2	1.5	2.71	1930	96	23.30
				44554	67.2	68.7	1.5	2.71	2270	101	23.98
				44555	68.7	70.2	1.5	2.71	2281	102	24.31
				44556	70.2	71.23	1.03	2.71	2004	96	21.98
71.23	72.53	100	BASALTIC ANDESITE Weakly SERPENTIZED ,	44557	71.23	72.53	1.3	2.76	133	48	12.35
72.53	75.0	100	SERPENTINITE Dark grey to black, visible stockworks of magnetite stringers and blebs and calc-talcy stringers.	44558	72.53	73.73	1.2	2.9	2004	98	21.28
				44559	73.73	75.0	1.28	2.9	2232	114	20.53
75.0	75.65	100	BASALTIC ANDESITE Weakly SERPENTIZED , non-magnetic, lower contact s 45° to c.a.	44560	75.0	75.65	0.65	2.76	340	55	16.66
75.65	76.8	100	SERPENTINITE Homogeneously black and dense moderately fragmented.	44561	75.65	76.8	1.15	2.65	2383	198	23.94
76.8	78.4	100	BASALTIC ANDESITE Weakly SERPENTIZED contains some black serpentinite intervals.	44562	76.8	78.4	1.6	2.65	682	66	16.36

DEPTH (meters) FROM TO		Recovery %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni %	Co ppm	Mg %
78.4	84.1	100	SERPENTINITE Homogeneously black and dense ; lower contact is broken, but assumed to be 45° to c.a.	44563 44564 44565 44566	78.4 79.9 81.4 82.9	79.9 81.4 82.9 84.1	1.5 1.5 1.5 1.2	2.65 2.65 2.65 2.65	2402 2234 1794 2119	118 90 88 99	23.71 23.68 21.52 23.92
84.1	88.2	100	ANDESITE/ BASALTIC ANDESITE Aphanitic, non-magnetic, with intervening serpentinite sections at: 85.7-86.0m 86.3-86.7m 87.2-87.95m	44567 44568 44569	84.1 85.3 86.8	85.3 86.8 88.2	1.2 1.5 1.4	2.78 2.78 2.78	551 602 229	66 63 42	12.01 12.11 5.38
88.2	114.2	100	DIORITE Medium grained, light greenish-grey, porphyroblastic with fractures that are totally coated with soft green soapstone, non-magnetic.	44570 44571 44572 44573 44574 44575 44576 44577 44578 44579 44580 44581 44582	88.2 90.2 92.2 94.2 96.2 98.2 100.2 102.2 104.2 106.2 108.2 110.2 112.2	90.2 92.2 94.2 96.2 98.2 100.2 102.2 104.2 106.2 108.2 110.2 112.2 114.2	2.0 2.0 2.0 2.0 2.0 2.0 2.0 2.0 2.0 2.0 2.0 2.0 2.0	2.7 2.7	120 320 135 83 121 112 105 126 102 140 129 123 97	26 37 28 30 32 25 24 26 26 30 29 25 24	2.53 5.56 2.61 3.18 3.80 2.36 1.99 2.20 2.10 3.17 2.87 2.61 2.55
114.2	115.0	100	SERPENTINITE Homogeneously black and dens and aphanitic Upper contact sharp 20° to c.a.; lower contact also sharp 20° to c.a; strongly magnetic This section was included in sample 44583								
115.0	117.9	100	BASALTIC ANDESITE Weakly serpentinized, non-magnetic, lower contact s 45° to c.a.	44583 44584	114.2 116.2	116.2 117.9	2.0 1.7	2.7 2.7	778 33	58 33	8.81 2.36
117.9	120.7	100	SERPENTINITE Homogeneously black same as previously	44585 44586	117.9 119.4	119.4 120.7	1.5 1.3		2262 2076	108 100	23.56 23.75

END OF HOLE

DIAMOND DRILL HOLE RECORD

PROPERTY: RECORD RIDGE SOUTH

DDH RRS08-16

DIP AND AZIMUTH TESTS			CORE SIZE: NQ	TOTAL DEPTH: 123.8m	DATE STARTED July 13, 2008
DEPTH	ANGLE	AZIMUTH	HOLE ANGLE: - 90°	HOLE AZIMUTH °	DATE FINISHED: July 15, 2008
123.7	-89.2°	295°	SECTION:	COLLAR ELEVATION: 1425.2m	ANALYSIS BY: Assayers Canada
			GRID LOCATION: 482S/ 1123W	RECOVERY:	LOGGED BY: H.K. & C.P.
			UTM (NAD 83): 5432407 N 434779 E	CLAIM: Frank Sr. 3	CORE STORED AT: Midnight camp

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm³)	Ni %	Co ppm	Mg %
0	0.7		Casing								
0.7	4.0	50	SERPENTINITE Fragmneted, milky-white to dark-grey, moderately magnetic, fractures are completely filled with soft, green, stealite soapstone.	44588 44589	0.7 2.0	2.0 4.0	1.3 2.0	2.62 2.62	1944 1856	103 90	18.52 18.70
4.0	13.75	100	SERPENTINITE Milky-white to dark-grey, moderately to strongly listwanized, calcite veins up to 2cm, 40° to c.a., contains mottled magnetite blebs.	44590 44591 44592 44593 44594 44595 44596	4.0 5.5 7.0 8.5 10.0 11.5 12.6	5.5 7.0 8.5 10.0 11.5 12.6 13.75	1.5 1.5 1.5 1.5 1.5 1.1 1.15	2.62 2.62 2.62 2.62 2.62 2.62 2.6	1613 1672 1906 2219 2247 1978 1534	73 71 91 107 114 98 68	17.37 17.60 19.42 23.78 23.15 20.77 19.46
13.75	26.95	100	BASALTIC ANDESITE Aphanitic with megascopic, sub-eudedral feldspar phenocrysts in a dark green to black matrix, dense; moderately chloritized; upper contact is sharp and 45° to c.a., lower contact is broken but assumed to be 45° to c.a.	44597 44598 44599 44600 44601 44602 44603	13.75 15.8 17.8 19.8 21.8 23.8 25.3	15.8 17.8 19.8 21.8 23.8 25.3 26.95	2.05 2.0 2.0 2.0 2.0 1.5 1.65	2.87 2.87 2.87 2.87 2.87 2.87 2.87	114 49 24 45 34 36 611	38 40 26 32 40 41 53	6.52 5.19 2.24 2.87 3.47 4.84 12.78
26.95	61.8	100	SERPENTINITE Homogeneously black, massive and strongly magnetic.	44604 44605 44606 44607 44608 44609 44610 44611 44612 44613 44614	26.95 28.5 30.0 31.5 33.0 34.5 36.0 37.5 39.0 40.5 42.0	28.5 30.0 31.5 33.0 34.5 36.0 37.5 39.0 40.5 42.0 43.5	1.55 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5	2.64 2.64 2.64 2.64 2.64 2.64 2.64 2.64 2.64 2.64 2.64	2258 1948 2032 2377 2236 2111 2470 2142 2070 1970 2171	99 88 87 99 96 91 105 96 92 87 93	21.14 22.16 23.37 22.60 23.30 23.27 23.46 23.02 21.66 21.88 21.98

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni %	Co ppm	Mg %
				44615	43.5	45.0	1.5	2.64	2217	99	24.13
				44616	45.0	46.5	1.5	2.64	2298	97	22.91
				44617	46.5	48.0	1.5	2.64	2389	99	23.38
				44618	48.0	49.5	1.5	2.64	2230	98	22.35
				44619	49.5	51.0	1.5	2.64	2190	94	23.72
				44620	51.0	52.5	1.5	2.64	2060	101	23.72
				44621	52.5	54.0	1.5	2.64	2076	100	22.69
				44622	54.0	55.5	1.5	2.64	1907	91	22.88
				44623	55.5	57.0	1.5	2.64	2261	100	24.11
				44624	57.0	58.5	1.5	2.64	2271	103	23.90
				44625	58.5	60.0	1.5	2.64	2144	98	23.44
				44626	60.0	61.8	1.8	2.64	2275	102	24.65
61.8	63.75	100	SERPENTINITE Dark green mixed with serpentized andesite, fractures are filled with soapstone.	44627	61.8	63.75	1.95	2.63	1756	93	19.47
63.75	65.8	100	SERPENTINITE Homogeneously black, massive and strongly magnetic.	44628	63.75	65.8	2.05	2.64	2193	102	22.64
65.8	69.5	100	MIXED SOAPSTONE & SERPENTINIZED ANDESITE	44629	65.8	67.6	1.8	2.78	1318	75	16.66
				44630	67.6	69.5	1.9	2.78	1206	72	15.46
69.5	77.15	100	SERPENTINITE Dark green to black with magnetic stockworks.	44631	69.5	71.0	1.5	2.66	1824	89	19.00
				44632	71.0	72.5	1.5	2.66	1966	93	19.79
				44633	72.5	74.0	1.5	2.66	2066	101	20.79
				44634	74.0	75.5	1.5	2.66	2190	103	21.66
				44635	75.5	77.15	1.65	2.66	2226	109	19.71
77.15	78.5	100	MIXED SOAPSTONE & SERPENTINIZED ANDESITE	44636	77.15	78.5	1.35	2.78	235	46	17.37
78.5	90.22	100	SERPENTINITE Homogeneously black, massive and strongly magnetic.	44637	78.5	80.0	1.5	2.58	2144	100	21.74
				44638	80.0	81.5	1.5	2.58	1917	100	21.09
				44639	81.5	83.0	1.5	2.58	1942	92	21.52
				44640	83.0	84.5	1.5	2.58	2079	88	21.82
				44641	84.5	86.0	1.5	2.58	2066	85	22.59
				44642	86.0	87.5	1.5	2.58	2048	90	22.55
				44643	87.5	89.0	1.5	2.58	2278	101	23.97
				44644	89.0	90.22	1.22	2.58	2031	101	22.63
90.22	104.85	100	SERPENTINITE Homogeneously black, massive and strongly magnetic, contains calcite veining at random intervals and orientations.	44645	90.22	91.7	1.48	2.58	2061	101	21.58
				44646	91.7	93.2	1.5	2.58	1984	95	19.76
				44647	93.2	94.7	1.5	2.58	2076	103	21.08
				44648	94.7	96.2	1.5	2.58	2177	109	22.73
				44649	96.2	97.7	1.5	2.58	2060	108	21.62
				44650	97.7	99.2	1.5	2.58	2233	110	22.44
				44651	99.2	100.7	1.5	2.58	2160	108	22.72

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni %	Co ppm	Mg %
				44652	100.7	102.2	1.5	2.58	2215	110	22.84
				44653	102.2	103.7	1.5	2.58	2061	104	22.03
				44654	103.7	104.85	1.15	2.58	2116	104	21.58
104.85	106.0	100	SOAPSTONE	44655	104.85	106.0	1.15	2.58	1787	83	17.63
106.0	118.3	100	BASALTIC ANDESITE/ DIAGABBRO Intervened with milky-white serpentinite intervals at: 108.1-108.8m 114.3-115.1m	44656	106.0	108.0	2.0	2.76	391	33	6.57
				44657	108.0	110.0	2.0	2.76	61	14	1.90
				44658	110.0	112.0	2.0	2.76	602	29	6.85
				44659	112.0	114.0	2.0	2.76	28	26	2.45
				44660	114.0	116.0	2.0	2.76	996	45	7.73
				44661	116.0	118.3	2.3	2.76	464	29	5.69
118.3	123.75	100	SERPENTINITE/SERPENTINIZED ANDESITE Lower 0.3m section is soft, pulverized soapstone.	44662	118.3	119.8	1.5	2.76	415	47	7.09
				44663	119.8	121.3	1.5	2.76	64	38	4.32
				44664	121.3	123.75	2.45	2.76	181	34	5.07

END OF HOLE

DIAMOND DRILL HOLE RECORD

PROPERTY: RECORD RIDGE SOUTH

DDH RRS08-17

DIP AND AZIMUTH TESTS			CORE SIZE: NQ	TOTAL DEPTH: 123.4 m	DATE STARTED July 15, 2008
DEPTH	ANGLE	AZIMUTH	HOLE ANGLE: - 90°	HOLE AZIMUTH °	DATE FINISHED: July 17, 2008
123.4	-88.6°	294°	SECTION:	COLLAR ELEVATION: 1430.4m	ANALYSIS BY: Assayers Canada
			GRID LOCATION: 425S/ 1125W	RECOVERY:	LOGGED BY: H.K. & C.P.
			UTM (NAD 83): 5432464N 434777E	CLAIM: Frank Sr. 3	CORE STORED AT: Midnight camp

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM M	TO m	Length m	P (g/cm ³)	Ni ppm	Co ppm	Mg %
0	0.8	100	CASING								
0.8	1.2	80	BOULDERS Monzonite and diorite								
1.2	2.5	100	SERPENTINITE Milky-white with magnetite stockworks	44665	1.2	2.5	1.3	2.66	1943	95	20.56
2.5	5.2	100	SERPENTINITE Compact hard, weakly to moderately magnetic.	44666 44667	2.5 3.8	3.8 5.2	1.3 1.4	2.66 2.66	2033 2029	103 104	22.19 22.00
5.2	16.55	100	SERPENTINITE Black, mottled with magnetite webs; section also contains some intervening sections of black homogeneous serpentinite.	44668 44669 44670 44671 44672 44673 44674 44675	5.2 6.7 8.2 9.7 11.2 12.7 12.7 14.2 15.3 15.3	6.7 8.2 9.7 11.2 12.7 14.2 15.3 16.55	1.5 1.5 1.5 1.5 1.5 1.5 1.1 1.25	2.66 2.66 2.66 2.66 2.66 2.66 2.66 2.66	2164 2070 2266 2287 2138 2148 2317 2171	103 98 107 116 112 109 116 106	22.62 21.87 21.58 23.28 23.04 22.03 22.62 21.44
16.55	23.85	100	SERPENTINIZED ANDESITE Fractures filled with soapstone.	44676 44677	16.55 18.0	18.0 19.5	1.45 1.5	2.7 2.7	274 336	47 52	18.77 19.71
19.5	22.5	100	SERPENTINITE. Milky white type	44678 44679	19.5 21.0	21.0 22.5	1.5 1.5	2.7 2.7	1844 1687	106 98	19.71 18.74
22.5	23.85	100	SERPENTINIZED ANDESITE Fractures filled with soapstone.	44680	22.5	23.85	1.35	2.7	724	70	19.61

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM M	TO m	Length m	P (g/cm ³)	Ni ppm	Co ppm	Mg %
23.85	38.56	100	SERPENTINITE Mottled and homogeneous black serpentinite. Serpentinized andesite from 36.0-37.3m	44681	23.85	25.4	1.55	2.66	2244	111	22.98
				44682	25.4	26.9	15	2.66	2306	114	24.33
				44683	26.9	28.4	1.5	2.66	2003	94	24.49
				44684	28.4	29.9	1.5	2.66	2127	101	22.96
				44685	29.9	31.4	1.5	2.66	2175	104	23.61
				44686	31.4	32.9	1.5	2.66	2304	103	24.10
				44687	32.9	34.4	1.5	2.66	2189	107	23.41
				44688	34.4	36.0	1.6	2.66	2157	108	23.29
				44689	36.0	37.3	1.3	2.66	1974	96	21.41
				44690	37.3	38.56	1.26	2.66	2213	119	24.60
38.56	48.3	100	SERPENTINITE Dark green, including some serpentinized andesite and soapstone at random intervals.	44691	38.56	40.0	1.44	2.66	2061	100	21.91
				44692	40.0	41.5	1.5	2.66	2077	101	21.52
				44693	41.5	43.0	1.5	2.66	2289	108	22.84
				44694	43.0	44.5	1.5	2.66	1903	89	19.49
				44695	44.5	46.0	1.5	2.66	1890	96	20.48
				44696	46.0	47.2	1.2	2.66	2057	103	20.97
				44697	47.2	48.3	1.1	2.66	1771	87	10.51
48.3	58.1	100	SERPENTINITE Black, mottled, magnetite stockwork, weakly listwanized.	44698	48.3	49.8	1.5	2.66	2461	116	23.78
				44699	49.8	51.3	1.5	2.66	2230	102	22.91
				44700	51.3	52.8	1.5	2.66	2240	90	21.37
				44701	52.8	54.3	1.5	2.66	1818	92	19.99
				44702	54.3	55.5	1.2	2.66	1956	105	20.16
				44703	55.5	56.55	1.05	2.66	2139	100	19.45
				44704	56.55	58.1	1.55	2.66	2023	108	16.85
58.1	77.1	100	BASALTIC ANDESITE/ DIAGABBRO 76.0-77.1m is serpentinized basaltic andesite.	44705	58.1	60.0	1.9	2.76	54	35	5.99
				44706	60.0	62.0	2.0	2.76	65	33	4.16
				44707	62.0	64.0	2.0	2.76	49	38	4.30
				44708	64.0	66.0	2.0	2.76	44	32	3.20
				44709	66.0	68.0	2.0	2.76	70	34	4.69
				44710	68.0	70.0	2.0	2.76	306	55	7.42
				44711	70.0	72.0	2.0	2.76	189	39	7.53
				44712	72.0	74.0	2.0	2.76	86	46	6.25
				44713	74.0	76.0	2.0	2.76	60	42	7.56
				44714	76.0	77.1	1.1	2.76	253	37	10.45
77.1	123.4	100	SERPENTINITE Mixed homogeneously black and dense serpentinite, conspicuously visible magnetite stockwork.	44715	77.1	78.6	1.5	2.64	2099	116	20.84
				44716	78.6	80.1	1.5	2.64	1899	107	19.41
				44717	80.1	81.6	1.5	2.64	1855	111	21.34
				44718	81.6	83.1	1.5	2.64	2143	124	23.76
				44719	83.1	84.6	1.5	2.64	2140	110	23.16
				44720	84.6	86.1	1.5	2.64	2043	126	24.59
				44721	86.1	87.6	1.5	2.64	2032	105	22.75
				44722	87.6	89.1	1.5	2.64	2089	103	24.00
				44723	89.1	90.6	1.5	2.64	1876	101	23.51
				44724	90.6	92.1	1.5	2.64	1863	99	23.18
				44725	92.1	93.6	1.5	2.64	2084	111	24.32

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM M	TO m	Length m	P (g/cm ³)	Ni ppm	Co ppm	Mg %
				44726	93.6	95.1	1.5	2.64	2157	109	24.42
				44727	95.1	96.6	1.5	2.64	2410	128	25.71
				44728	96.6	98.1	1.5	2.64	2042	110	23.38
				44729	98.1	99.6	1.5	2.64	2102	115	23.16
				44730	99.6	101.1	1.5	2.64	1969	105	22.88
				44731	101.1	102.6	1.5	2.64	2190	114	23.82
				44732	102.6	104.1	1.5	2.64	2154	120	23.52
				44733	104.1	105.6	1.5	2.64	1497	85	19.04
				44734	105.6	107.1	1.5	2.64	1967	106	24.31
				44735	107.1	108.6	1.5	2.64	1896	95	22.66
				44736	108.6	110.1	1.5	2.66	2128	100	22.22
				44737	110.1	111.6	1.5	2.66	2116	104	24.13
				44738	111.6	113.1	1.5	2.66	2153	100	23.59
				44739	113.1	114.6	1.5	2.66	2115	96	23.87
				44740	114.6	116.1	1.5	2.66	2101	86	21.40
				44741	116.1	117.6	1.5	2.66	2093	65	22.33
				44742	117.6	118.7	1.1	2.66	1963	84	21.57
				44743	118.7	120.2	1.5	2.66	1023	75	13.99
				44744	120.2	121.7	1.5	2.66	1316	62	14.58
				44745	121.7	123.4	1.7	2.66	1008	54	12.70

END OF HOLE

DIAMOND DRILL HOLE RECORD

PROPERTY: RECORD RIDGE SOUTH

DDH RRS08-18

DIP AND AZIMUTH TESTS			CORE SIZE: NQ	TOTAL DEPTH: 122.22m	DATE STARTED: July 17, 2008
DEPTH	ANGLE	AZIMUTH	HOLE ANGLE: - 90°	HOLE AZIMUTH °	DATE FINISHED: July 21, 2008
122.2	-89.7°	299°	SECTION: 1175W/ 400S	COLLAR ELEVATION: 1447.7m	ANALYSIS BY: Assayers Canada
			GRID LOCATION: W / S	RECOVERY:	LOGGED BY: H.K. & C.P.
			UTM (NAD 83): 5432489N 434727E	CLAIM: Frank Sr. 3	CORE STORED AT: Midnight camp

DEPTH (meters) FROM TO		Recovery (%)	Description	Sample No.	From (m)	To (m)	Length (m)	P (g/cm³)	Ni (%)	Co (ppm)	Mg (%)
			Casing to 0.6 m								
0.6	20.4	98	SERPENTINITE Greenish to grey to dark green; mottled streaks and blebs of magnetite 0.5 – 5.5 : moderately fragmented with limonitized fractures Pet sample at 6.1 m	44746	0.6	2.1	1.5	2.8	2258	110	25.21
				44747	2.1	3.6	1.5	2.8	2074	106	24.02
				44748	3.6	5.1	1.5	2.8	2213	112	25.54
				44749	5.1	6.6	1.5	2.8	2336	112	26.01
				44750	6.6	8.1	1.5	2.8	2103	106	24.92
				44751	8.1	9.6	1.5	2.8	2215	109	25.54
				44752	9.6	11.1	1.5	2.8	2368	114	26.28
				44753	11.1	12.6	1.5	2.8	2381	112	25.99
				44754	12.6	14.1	1.5	2.8	2236	109	24.98
				44755	14.1	15.6	1.5	2.8	2142	105	24.28
				44756	15.6	17.1	1.5	2.8	2199	108	24.28
				44757	17.1	18.6	1.5	2.8	2169	107	23.89
				44758	18.6	20.4	1.8	2.8	2109	105	24.26
20.4	31.0	100	SERPENTINITE Fairly similar to the previous section except darker green coloration without visible listwanization	44759	20.4	21.9	1.5	2.8	2195	111	25.50
				44760	21.9	23.4	1.5	2.8	2289	111	25.24
				44761	23.4	24.9	1.5	2.8	2323	115	25.65
				44762	24.9	26.4	1.5	2.8	2401	115	25.72
				44763	26.4	27.9	1.5	2.8	2281	116	25.60
				44764	27.9	29.4	1.5	2.8	2311	114	25.28
				44765	29.4	31.0	1.6	2.8	2211	108	24.52
31.0	39.2	100	SERPENTINITE Dark grey to black ; pronounced webs of calcite veinlets, 1 – 5 mm ; upper contact gradational but assumed to be 45° to c.a.	44766	31.0	32.5	1.5	2.8	1963	103	21.30
				44767	32.5	34.0	1.5	2.8	1427	83	19.48
				44768	34.0	35.5	1.5	2.8	1932	97	22.08
				44769	35.5	37.0	1.5	2.65	1947	94	21.66
				44770	37.0	38.1	1.1	2.65	2020	100	22.42
				44771	38.1	39.2	1.1	2.65	1708	85	19.37

DEPTH (meters) FROM TO		Recovery (%)	Description	Sample No.	From (m)	To (m)	Length (m)	P (g/cm ³)	Ni (%)	Co (ppm)	Mg (%)
39.2	46.7	100	SERPENTINITE Dark grey to black; mottled magnetite blebs and webbed streaks Pet sample at 40.7	44772 44773 44774 44775 44776	39.2 40.7 42.2 43.7 45.2	40.7 42.2 43.7 45.2 46.7	1.5 1.5 1.5 1.5 1.5	2.65 2.65 2.65 2.65 2.65	2211 2139 2128 2150 2042	107 106 101 107 99	23.67 24.32 23.61 23.35 21.57
46.7	50.1	100	SERPENTINIZED ANDESITE 17.08 18.45 Light green, dense, hard, compact, but can be scratched easily, non-magnetic	44777 44778	46.7 48.2	48.2 50.1	1.5 1.9	2.56 2.56	781 1142	62 68	9.19 12.79
50.1	52.6	100	SERPENTINITE Dark green, strongly magnetic, conspicuous magnetite webs.	44779 44780	50.1 51.3	51.3 52.6	1.2 1.3	2.56 2.56	1627 1886	87 93	17.08 18.45
52.6	57.6	100	SERPENTINIZED ANDESITE Mixed with greenish serpentinite Greenish-grey, non-magnetic, upper contact is gradational but assumed to be 45° to c.a. Petrographic sample at 55.8m	44781 44782 44783	52.6 54.1 55.6	54.1 55.6 57.6	1.5 1.5 2.0	2.76 2.76 2.76	480 1227 1166	69 91 79	16.35 17.01 17.07
57.6	67.2	100	SERPENTINITE Homogeneously black, dense, strongly magnetic.	44784 44785 44786 44787 44788 44789 44790	57.6 59.1 60.6 62.1 63.6 65.1 66.1	59.1 60.6 62.1 63.6 65.1 66.1 67.2	1.5 1.5 1.5 1.5 1.5 1.0 1.1	2.65 2.65 2.65 2.65 2.65 2.65 2.65	1972 1955 1991 1980 1808 2010 1975	105 105 108 105 100 112 108	22.43 23.40 23.58 23.60 22.23 22.85 21.32
67.2	71.6	100	SERPENTINIZED DIAGABBRO(?) Greenish-grey, non-magnetic, upper contact is completely serpentinitized.	44791 44792 44793	67.2 68.7 70.2	68.7 70.2 71.6	1.5 1.5 1.4	2.76 2.76 2.76	156 71 1256	45 41 93	9.78 7.20 13.65
71.6	108.6	100	MONZODIORITE TO MONZOGABBRO Aphanitic to fine-grained, greenish-grey to dark-grey, includes serpentinitized sections at 83.6 – 87.6 , however, 90% of the core section is sub- intrusive rocks, upper contact is totally serpentinitized, lower contact is serpentinitized and 45° to c.a. Petrographic sample at 90.2m	44794 44795 44796 44797 44798 44799 44800 44801 44802 44803 44804 44805 44806 44807 44808	71.6 73.6 75.6 77.6 79.6 81.6 83.6 85.6 87.6 89.6 91.6 93.6 95.6 97.6 99.6	73.6 75.6 77.6 79.6 81.6 83.6 85.6 87.6 89.6 91.6 93.6 95.6 97.6 99.6 101.6	1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5	2.76 2.76 2.76 2.76 2.76 2.76 2.76 2.76 2.76 2.76 2.76 2.76 2.76 2.76 2.76	28 22 20 23 34 639 1517 1074 40 61 26 27 12 34 54	30 32 33 38 40 54 73 58 29 30 33 33 18 35 45	2.63 3.38 3.29 4.30 5.72 6.42 8.41 5.38 1.73 3.09 3.59 3.76 2.99 3.19 5.58

DEPTH (meters) FROM TO		Recovery (%)	Description	Sample No.	From (m)	To (m)	Length (m)	P (g/cm ³)	Ni (%)	Co (ppm)	Mg (%)
108.6	122.22	100	SERPENTINITE Homogeneously black, dense, strongly magnetic. Note: No sampling was done in this section, which is overlain by thick succession of monzodiorite, over 37 m								

END OF HOLE

DIAMOND DRILL HOLE RECORD

PROPERTY: RECORD RIDGE SOUTH

DDH RRS08-19

DIP AND AZIMUTH TESTS			CORE SIZE: NQ	TOTAL DEPTH: 63.5 m	DATE STARTED July 21, 2008
DEPTH	ANGLE	AZIMUTH	HOLE ANGLE: - 90°	HOLE AZIMUTH °	DATE FINISHED: July 23, 2008
62.8	-89.1°	143°	SECTION:	COLLAR ELEVATION: 1458.6m	ANALYSIS BY: Assayers Canada
			GRID LOCATION: 425S/ 1225W	RECOVERY:	LOGGED BY: H.K. & C.P.
			UTM (NAD 83): 5432464N 434677E	CLAIM: Frank Sr. 3	CORE STORED AT: Midnight camp

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni ppm	Co ppm	Mg %
0	0	100	Casing								
0.0	3.3	100	SERPENTINITE Dark grey to black with stockworks of magnetite streaks.	44809 44810	0.0 1.6	1.6 3.3	1.6 1.7	2.65 2.65	2248 2266	120 103	23.96 24.35
3.3	16.1	100	SERPENTINITE Homogeneously black, dense, lower contact is 45° to c.a.	44811 44812 44813 44814 44815 44816 44817 44818 44819	3.3 4.8 6.3 7.8 9.3 10.8 12.3 13.8 15.3	4.8 6.3 7.8 9.3 10.8 12.3 13.8 15.3	1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 0.8	2.65 2.65 2.65 2.65 2.65 2.65 2.65 2.65 2.65	2112 2171 2281 2224 2094 2140 2290 2252 2304	93 95 99 104 97 98 104 103 106	22.97 23.71 23.85 24.52 24.17 24.02 24.66 24.75 23.58
16.1	18.0	100	SERPENTINE Soft light greenish-grey, talcy.	44820	16.1	18.0	1.9	2.78	1310	82	16.89
18.0	28.2	100	SERPENTINITE Homogeneously black, dense	44821 44822 44823 44824 44825 44826 44827	18.0 19.5 21.0 22.5 24.0 25.5 27.0	19.5 21.0 22.5 24.0 25.5 27.0 28.2	1.5 1.5 1.5 1.5 1.5 1.5 1.2	2.65 2.65 2.65 2.65 2.65 2.65 2.65	2232 2191 2090 2091 2226 2266 2183	99 103 107 108 104 104 109	24.00 24.22 23.32 23.58 23.93 24.18 23.41
28.2	30.2	100	BASALTIC ANDESITE/ DIAGABBRO Weakly serpentized.	44828 44829	28.2 29.2	29.2 30.2	1.0 1.0	2.65 2.65	147 28	30 27	6.25 6.00
30.2	36.0	100	SERPENTINITE Dark greenish-grey with soft light green serpentine sections at random intervals.	44830 44831 44832	30.2 31.7 33.2	31.7 33.2 34.7	1.5 1.5 1.5	2.65 2.65 2.65	1817 1428	90 77	20.30 19.49 23.25

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni ppm	Co ppm	Mg %
				44833	34.7	36.0	1.3	2.65	1683	78	18.91
36.0	48.1	100	SERPENTINITE Homogeneously black, dense,	44834 44835 44836 44837 44838 44839 44840 44841	36.0 37.5 39.0 40.5 42.0 43.5 45.0 46.5	37.5 39.0 40.5 42.0 43.5 45.0 46.5 48.1	1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.6	2.65 2.65 2.65 2.65 2.65 2.65 2.65 2.65	2291 2158 2241 2152 2258 2148 2335 2293	98 102 105 105 104 100 107 111	24.14 23.76 24.40 23.88 23.99 22.54 24.79 23.01
48.1	50.6	100	SERPENTINITE Dark grey with sporadic soapstone fractures and magnetite webs with calcite veinlets.	44842 44843	48.1 49.6	49.6 50.6	1.5 1.0	2.65 2.65	1445 1933	84 90	20.68 21.94
50.6	55.5	100	SERPENTINITE Homogeneously black, dense, with sporadic soft serpentinized fractures	44844 44845 44846	50.6 52.1 53.6	52.1 53.6 55.5	1.5 1.5 1.9	2.65 2.65 2.65	2175 2620 2112	102 117 98	24.27 27.49 22.84
55.5	57.1	100	SERPENTINE Dark green, soft, pulverized	44847	55.5	57.1	1.6	2.65	1889	92	21.62
57.1	59.2	100	SERPENTINITE Dark grey with magnetite sockwork, lower contact is sharp and 45° to c.a.	44848 44849	57.1 58.1	58.1 59.2	1.0 1.1	2.65 2.65	2054 2121	98 100	22.56 21.98
59.2	60.8	100	SERPENTINITE; moderately serpentinized Light greenish-grey, compact, hard, can be scratched readily (soft).	44850	59.2	60.8	1.6	2.65	1383	68	15.10
60.8	63.5	100	BASALTIC ANDESITE/ DIAGABBRO Light greenish-grey, aphanitic to fine-grained.	44851	60.8	62.3	1.5	2.78	358	49	7.50

END OF HOLE

DIAMOND DRILL HOLE RECORD

PROPERTY: RECORD RIDGE SOUTH

DDH RRS08-20

DIP AND AZIMUTH TESTS			CORE SIZE: NQ	TOTAL DEPTH: 30.2m	DATE STARTED July 22, 2008
DEPTH	ANGLE	AZIMUTH	HOLE ANGLE: - 90°	HOLE AZIMUTH °	DATE FINISHED: July 23, 2008
	°	000°	SECTION:	COLLAR ELEVATION: 1463.4m	ANALYSIS BY: Assayers Canada
			GRID LOCATION: 400S/ 1275W	RECOVERY:	LOGGED BY: H.K. & C.P.
			UTM (NAD 83): 5432489N 434627E	CLAIM: Frank Sr. 3	CORE STORED AT: Midnight camp

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm³)	Ni %	Co ppm	Mg %
0	6.7		CASING								
6.7	8.1	42	FAULTED SHEAR ZONE Mixed dark green serpentinite and rusted, fragmented and pulverized serpentinite.	44852 44853 44854	0.0 4.9 6.7	4.9 6.7 8.1	4.9 1.8 1.4	n/a n/a n/a	1446 570 647	85 49 60	16.35 5.85 9.69
8.1	18.9	100	SERPENTINITE Mixed homogeneously black serpentinite (80%) and dark grey serpentinite (20%) with visible magnetite stockworks, lower contact is mushy serpentine.	44855 44856 44857 44858 44859 44860 44861	8.1 9.6 11.1 12.6 14.1 15.6 17.1	9.6 11.1 12.6 14.1 15.6 17.1 18.9	1.5 1.5 1.5 1.5 1.5 1.5 1.8	2.8 2.8 2.8 2.8 2.8 2.8 2.8	2012 2163 2026 2179 2364 2221 2166	95 107 103 108 112 106 103	19.92 22.86 22.01 23.37 24.24 23.43 22.59
18.9	20.2	80	SERPENTINE Greenish-grey, soft, highly fragmented to pulverized.	44862	18.9	20.2	1.3	n/a	369	52	11.37
20.2	27.5	100	SERPENTINITE Dark green, aphanitic, weakly magnetic with strongly magnetic sections, visible stockworks of magnetite streaks and blebs. Lower contact is broken and highly serpentinized.	44863 44864 44865 44866 44867	20.2 21.7 23.2 24.7 26.2	21.7 23.2 24.7 26.2 27.5	1.5 1.5 1.5 1.5 1.3	2.8 2.8 2.8 2.8 2.8	1298 2047 1800 2260 2034	78 96 86 108 99	15.80 18.79 18.96 24.52 22.97
27.5	38.4	100	BASALTIC ANDESITE With soapstone fractures. Upper 0.3m is totally serpentinized and fragmented.	44868 44869	27.5 29.0	29.0 30.2	1.5 1.2		193 495	44 52	6.41 7.58

END OF HOLE

DIAMOND DRILL HOLE RECORD

PROPERTY: RECORD RIDGE SOUTH

DDH RRS08-21

DIP AND AZIMUTH TESTS			CORE SIZE: NQ	TOTAL DEPTH: 116.7 m	DATE STARTED: July 24, 2008
DEPTH	ANGLE	AZIMUTH	HOLE ANGLE: - 90°	HOLE AZIMUTH °	DATE FINISHED: July 28, 2008
116.7m	-89.4°	264.5°	SECTION:	COLLAR ELEVATION: 1476.1m	ANALYSIS BY: Assayers Canada
			GRID LOCATION:1375W / 450S	RECOVERY:	LOGGED BY: H.K. & C.P.
			UTM (NAD 83): 5432439N 434527E	CLAIM: Frank Sr. 3	CORE STORED AT: Midnight camp

DEPTH (meters) FROM TO		Recovery (%)	Description	Sample No.	From (m)	To (m)	Length (m)	P (g/cm ³)	Ni (%)	Co (ppm)	Mg (%)	Cr (%)
			Casing to 1.5m									
0	0.7	90	SERPENTINITE Dark grey with magnetite stockwork; weakly limonitized and moderately magnetic	44870	0	1.1	1.1	2.65	2056	98	21.91	
0.7	4.65	90	FAUL ZONE IN SERPENTINITE 0.7 – 1.1 : fault gouge 1.1 – 4.7: highly fragmented dark grey serpentinite with magnetite stockwork same as previously	44871 44872	1.1 2.6	2.6 4.65	1.5 2.05	2.65 2.65	2211 1674	106 81	23.01 16.90	
4.7	5.25	100	ANDESITE Light greenish grey, aphanitic, non-magnetic; Upper contact broken; Lower contact also broken but assuming 40° to c.a. * Included in sample 55873				0.55	2.72				
5.25	11.0	100	SERPENTINITE Black and dense with calcite veinlets generally oriented 0° to c.a	44873 44874 44875 44876	4.65 6.2 7.7 9.2	6.2 7.7 9.2 11.0	1.55 1.5 1.5 1.8	2.65 2.65 2.65 2.65	1384 2175 2249 2615	79 103 103 111	15.44 22.98 23.47 24.33	
11.0	29.5	100	SERPENTINITE Generally homogeneously black and dense without calcite veinlets 19.0 – 23.0 : sporadic calcite veinlets at random intervals	44877 44878 44879 44880 44881 44882 44883 44884 44885 44886 44887	11.0 12.5 14.0 15.5 17.0 18.5 20.0 21.5 23.0 24.5 26.0	12.5 14.0 15.5 17.0 18.5 20.0 21.5 23.0 24.5 26.0 27.5	1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5	2.8 2.8 2.8 2.8 2.8 2.8 2.8 2.8 2.8 2.8 2.8	2293 2391 2101 2145 2003 1970 2065 1908 2141 2036 2050	107 110 103 100 106 111 108 104 108 105 103	24.74 25.38 23.33 24.36 23.86 23.38 25.37 24.34 25.28 24.76 24.30	 0.23 0.25 0.24 0.21 0.29 0.30 0.24

DEPTH (meters) FROM TO		Recovery (%)	Description	Sample No.	From (m)	To (m)	Length (m)	P (g/cm ³)	Ni (%)	Co (ppm)	Mg (%)	Cr (%)
				44888	27.5	29.5	2.0	2.8	2230	117	24.89	0.26
929.5	32.95	100	BASALTIC ANDESITE Upper contact sharp 45° to c.a. Also upper 0.8 m section is totally serpentinized; greasy and silky luster; Lower 0.3 m section is also serpentinized same as previously	44889 44890	29.5 31.0	31.0 32.5	1.5 1.5	2.76 2.76	203 42	44 42	5.33 3.99	0.04 0.02
32.95	34.11	100	SERPENTINITEZED BASALTIC ANDESITE Basaltic andesite moderately serpentinized with greasy and silky luster	44891	32.5	34.11	1.61	2.76	1063	80	14.83	0.17
34.11	58.9	100	SERPENTINITE Homogenously black and dense Sporadically visible magnetic stockwork at random intervals at 52.0 – 58.0	44892 44893 44894 44895 44896 44897 44898 44899 44900 44901 44902 44903 44904 44905 44906 44907	34.11 35.6 37.1 38.6 40.1 41.6 43.1 44.6 46.1 47.6 49.1 50.6 52.1 53.6 55.1 56.6	35.6 37.1 38.6 40.1 41.6 43.1 44.6 46.1 47.6 49.1 50.6 52.1 53.6 55.1 58.9	1.49 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 2.3	2.8 2.8 2.8 2.8 2.8 2.8 2.8 2.8 2.8 2.8 2.8 2.8 2.65 2.65 2.65 2.65	1906 2059 1966 1947 2169 1983 1931 2017 1939 2371 2259 2591 2525 2311 2143 2433	108 114 114 111 112 110 108 112 109 112 108 117 120 110 109 122	23.39 25.08 24.17 24.32 24.94 24.08 24.76 24.68 25.18 24.67 23.45 26.42 27.12 24.75 22.49 25.44	0.27 0.30 0.28 0.30 0.21 0.28 0.23 0.37 0.42
58.9	64.9	100	MIXED SERPENTINE & BASALTIC ANDESITE Serpentine is soft and highly broken, top contact is sharp and 45° to c.a. (toaly serpentinized).	44908 44909 44910	58.9 60.9 62.9	60.9 62.9 64.9	2.0 2.0 2.0	2.76 2.76 2.76	286 942 117	39 67 31	9.1 10.2 5.4	
64.9	71.05	100	BASALTIC ANDESITE/ DIAGABBRO Aphaniti to fine-grained, sub-euhedral to euhedral feldspar phenocrysts set in a greenish-grey matrix, upper contact is broken and serpentinized.	44911 44912 44913	64.9 66.9 68.9	66.9 68.9 71.05	2.0 2.0 2.15	2.76 2.76 2.76	08 37 36	46 30 30	2.5 1.9 2.4	
71.05	71.5	100	SULPHIDE-RICH BASALTIC ANDESITE Chalcopyrite /pyrite patches up to 10 cm long with calcite/ quartz veinlets.	44914	71.05	71.5	0.45	2.76	62	117	2.4	
71.5	72.4	100	SERPENTINITEZED BASALTIC ANDESITE Contains calc-quartz veins that run parallel to c.a., lower contact is 45° to c.a.	44915	71.5	72.4	0.9	2.76	35	34	2.6	

DEPTH (meters) FROM TO		Recovery (%)	Description	Sample No.	From (m)	To (m)	Length (m)	P (g/cm ³)	Ni (%)	Co (ppm)	Mg (%)	Cr (%)
72.4	89.8	100	BASALTIC ANDESITE/ DIAGABBRO Lower contact is serpentinized and 70° to c.a.	44916	72.4	74.4	2.0	2.76	23	21	2.2	
				44917	74.4	76.4	2.0	2.76	24	25	2.1	
				44918	76.4	78.4	2.0	2.76	34	30	2.4	
				44919	78.4	80.4	2.0	2.76	44	31	3.0	
				44920	80.4	82.4	2.0	2.76	13	31	3.7	
				44921	82.4	84.4	2.0	2.76	6	23	2.0	
				44922	84.4	86.4	2.0	2.76	27	27	2.3	
				44923	86.4	88.4	2.0	2.76	28	25	2.3	
				44924	88.4	89.8	1.4	2.76	107	30	2.9	
89.8	97.9	100	SERPENTINITE Homogenously black and dense Sporadically visible magnetic stockwork.	44925	89.8	91.3	1.5	2.65	2059	105	22.77	
				44926	91.3	92.8	1.5	2.65	2270	105	24.68	
				44927	92.8	94.3	1.5	2.65	2179	105	23.93	
				44928	94.3	95.8	1.5	2.65	2322	111	25.11	
				44929	95.8	97.9	2.1	2.65	2153	102	22.91	
97.9	100.2	100	FRAGMENTED BASALTIC ANDESITE Weakly serpentinized.	44930	97.9	100.2	2.3	2.76	178	36	4.6	
100.2	101.9	100	BASALTIC ANDESITE	44931	100.2	101.9	1.7	2.76	29	32	3.0	
101.9	102.9	100	FRAGMENTED ANDESITE Weakly serpentinized.	44932	101.9	102.9	1.0	2.76	24	33	3.3	
102.9	116.7	100	BASALTIC ANDESITE/ DIAGABBRO Solid intact, massive except for some sporadic, short serpentinized and fragmented sections at random intervals.	44933	102.9	104.9	2.0	2.76	38	29	2.9	
				44934	104.9	106.9	2.0	2.76	39	28	2.9	
				44935	106.9	108.9	2.0	2.76	44	32	3.7	
				44936	108.9	110.9	2.0	2.76	22	29	3.0	
				44937	110.9	112.9	2.0	2.76	32	29	4.4	
				44938	112.9	114.9	2.0	2.76	27	27	3.5	
				44939	114.9	116.7	1.8	2.76	14	24	3.4	

END OF HOLE

DIAMOND DRILL HOLE RECORD

PROPERTY: Ivanhoe Ridge

RECORD RIDGE SOUTH

DDH RRS08-22

PAGE: OF

DIP AND AZIMUTH TESTS			CORE SIZE: NQ	TOTAL DEPTH: 29.3m	DATE STARTED July 28, 2008
DEPTH	ANGLE	AZIMUTH	HOLE ANGLE: - 90°	HOLE AZIMUTH °	DATE FINISHED: July 29, 2008
			SECTION:	COLLAR ELEVATION: 1463.5m	ANALYSIS BY: Assayers Canada
			GRID LOCATION: 350S/ 1275W	RECOVERY:	LOGGED BY: H.K. & C.P.
			UTM (NAD 83): 5432539N 434627E	CLAIM: Frank Sr. 3	CORE STORED AT: Midnight camp

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni %	Co ppm	Mg %	Cr %	Pd g/t	Pt g/t	Ag g/t	Au g/t
0	3.7		Casing													
3.7	5.2	50	FAULTED/ SHEARED ZONE Finely fragmented cores consisting of light greenish-grey andesite & aphanitic, non-magnetic basaltic andesite.	44940	4.0	5.2	1.2	2.86	47	25	2.1					
5.2	29.3	100	GABBRO TO DIAGABBRO Medium grained, greenish-black, equigranular, 70% of the mafic phenocrysts are chloritized, mottled by calcite blebs, overall weakly magnetic. • Petrographic sample @ 7.5m	44941 44942 44943 44944 44945 44946 44947 44948 44949 44950	5.2 7.0 9.0 11.0 13.0 15.0 17.0 19.0 21.0 23.0	7.0 9.0 11.0 13.0 15.0 17.0 19.0 21.0 23.0 25.0	2.0 2.0 2.0 2.0 2.0 2.0 2.0 2.0 2.0 2.0	2.86 2.86 2.86 2.86 2.86 2.86 2.86 2.86 2.86 2.86	39 40 40 45 44 42 41 42 41 44	27 28 28 28 28 30 29 30 30 31	2.3 2.4 2.5 3.1 3.5 2.9 2.9 3.0 2.9 3.2					

END OF HOLE

DIAMOND DRILL HOLE RECORD

PROPERTY: RECORD RIDGE SOUTH

DDH RRS08-23

DIP AND AZIMUTH TESTS			CORE SIZE: NQ	TOTAL DEPTH: 152.4m	DATE STARTED July 29, 2008
DEPTH	ANGLE	AZIMUTH	HOLE ANGLE: - 90°	HOLE AZIMUTH °	DATE FINISHED: August 6, 2008
152.4m	-89.1°	184.1°	SECTION:	COLLAR ELEVATION: 1491.7m	ANALYSIS BY: Assayers Canada
			GRID LOCATION: 225S/ 1325W	RECOVERY:	LOGGED BY: H.K. & C.P.
			UTM (NAD 83): 5432664N 434577E	CLAIM: Frank Sr. 3	CORE STORED AT: Midnight camp

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm³)	Ni %	Co ppm	Mg %
0	5.2		Casing								
5.2	7.9	100	SERPENTINITE Homogeneously black, dense, strongly magnetic.	45001 45002	5.2 6.5	6.5 7.9	1.3 1.4	2.65 2.65	2115 2213	103 100	22.39 22.90
7.9	28.6	100	MONZOSYENITE Euohedral to sub-euohedral feldspar phenocrysts up to 7mm, also biotite flecks up to 3mm long set in a light-grey, medium-grained (with some pinkish hues) groundmass. Upper contact is sharp and healed with green serpentine and 45° to c.a., lower contact is also 45° to c.a. with serpentinized fractures. Petrographic sample @ 12.8m	45003 45004 45005 45006 45007 45008 45009 45010 45011 45012	7.9 10.0 12.0 14.0 16.0 18.0 20.0 22.0 24.0 26.0	10.0 12.0 14.0 16.0 18.0 20.0 22.0 24.0 26.0 28.6	2.1 2.0 2.0 2.0 2.0 2.0 2.0 2.0 2.0 2.6	2.7 2.7 2.7 2.7 2.7 2.7 2.7 2.7 2.7 2.7	42 39 26 25 24 21 24 20 23 45	20 21 21 21 20 18 20 22 20 19	2.8 2.6 1.8 1.8 1.7 1.6 1.8 2.0 1.7 3.5
28.6	41.7	100	SERPENTINITE Black with calcite veinlets that run through core at 50° to c.a. 32.8-32.85m is fault gouged. 37.6-38.4m is soft green serpentine 41.3-41.7m is green gouge.	45013 45014 45015 45016 45017 45018 45019 45020 45021	28.6 30.1 31.6 33.1 34.6 36.1 37.6 39.1 40.6	30.1 31.6 33.1 34.6 36.1 37.6 39.1 40.6 41.7	1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.1	2.63 2.63 2.63 2.63 2.63 2.63 2.63 2.63 2.63	1214 2275 2308 2295 1992 1838 1668 1990 1807	60 108 111 111 106 98 92 110 100	13.18 22.18 22.73 22.99 20.93 16.69 19.40 22.62 22.13
41.7	103.1	100	SERPENTINITE Black and fine-grained, also dense at random intervals. Contains megascopically conspicuous "silver-looking" metal flakes up to 1-2%; solid intact cores throughout the section Looks very similar to the upper	45022 45023 45024 45025 45026 45027	41.7 43.2 44.7 46.2 47.7 49.2	43.2 44.7 46.2 47.7 49.2 50.7	1.5 1.5 1.5 1.5 1.5 1.5	2.63 2.63 2.63 2.63 2.63 2.63	2043 1958 1895 1821 1883 1885	108 105 101 101 102 102	24.31 24.70 23.41 23.46 23.06 23.80

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni %	Co ppm	Mg %
			outcrop wehrlite grab sample that was taken. • Petrographic sample @ 47.3m	45028	50.7	52.2	1.5	2.63	1706	100	24.01
				45029	52.2	54.0	1.5	2.63	2061	107	24.06
				45030	54.0	55.5	1.5	2.63	1899	105	23.48
				45031	55.5	57.0	1.5	2.63	2002	106	24.33
				45032	57.0	58.5	1.5	2.63	1991	106	24.03
				45033	58.5	60.0	1.5	2.63	1937	101	23.05
				45034	60.0	61.5	1.5	2.63	1924	103	23.22
				45035	61.5	63.0	1.5	2.63	1989	108	25.50
				45036	63.0	64.5	1.5	2.63	1900	109	24.40
				45037	64.5	66.0	1.5	2.63	2009	115	24.46
				45038	66.0	67.5	1.5	2.63	1990	105	23.80
				45039	67.5	69.0	1.5	2.63	2064	96	22.84
				45040	69.0	70.5	1.5	2.70	1911	96	22.98
				45041	70.5	72.0	1.5	2.70	2173	98	24.12
				45042	72.0	73.5	1.5	2.80	2243	103	24.67
				45043	73.5	75.0	1.5	2.80	2298	108	24.44
				45044	75.0	76.5	1.5	2.80	2338	110	24.92
				45045	76.5	78.0	1.5	2.80	2393	111	24.74
				45046	78.0	79.5	1.5	2.80	2261	105	24.27
				45047	79.5	81.0	1.5	2.80	2315	110	25.36
				45048	81.0	82.5	1.5	2.80	2334	111	25.38
				45049	82.5	84.0	1.5	2.80	2346	115	24.96
				45050	84.0	85.5	1.5	2.80	2347	119	25.28
				45051	85.5	87.0	1.5	2.80	2441	120	25.77
				45052	87.0	88.5	1.5	2.80	2429	119	24.86
				45053	88.5	90.0	1.5	2.80	2401	118	25.22
				45054	90.0	91.5	1.5	2.80	2696	121	26.69
				45055	91.5	93.0	1.5	2.80	2441	121	25.41
				45056	93.0	94.5	1.5	2.80	2423	115	24.98
				45057	94.5	96.0	1.5	2.80	2351	110	25.62
				45058	96.0	97.5	1.5	2.80	2327	115	25.73
				45059	97.5	99.0	1.5	2.80	2460	116	24.93
				45060	99.0	100.5	1.5	2.80	2325	113	24.11
				45061	100.5	102.0	1.5	2.80	2104	108	24.09
				45062	102.0	103.1	1.5	2.80	2192	111	23.95
103.1	105.1	100	SERPENTINITE, Fragmented Also homogeneously black and dense fairly similar to previous section except moderately fragmented (some sheared) with fractures healed with green soft serpentine; weak to moderately magnetic	45063	103.1	105.1	2.0	n/a	2247	115	24.43
105.1	109.85	100	SERPENTINITE Black and fine-grained, also dense at random intervals, similar to the previous section at	45064	105.1	106.5	1.5	2.8	2016	106	23.17
				45065	106.5	108.0	1.5	2.8	1973	102	22.79
				45066	108.0	109.85	1.5	2.8	2168	105	22.84

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni %	Co ppm	Mg %
			41.1- 103.1								
109.85	110.5	100	SERPENTINIZED ANDESITE Greenish-grey, non-magnetic, aphanitic to fine-grained, upper & lower contacts are sharp and 45° to c.a.	45067	109.85	110.5	0.65	2.74	81	34	4.0
110.5	152.4	100	SERPENTINITE Black and fine-grained, also dense at random intervals. Contains megascopically conspicuous “silver-looking” metal flakes up to 1-2%, solid intact cores throughout the section.	45068	110.5	112.0	1.5	2.6	2008-	98	22.74
				45069	112.0	113.5	1.5	2.6	2008	95	22.81
				45070	113.5	115.0	1.5	2.7	2178	100	22.67
				45071	115.0	116.5	1.5	2.7	2017	94	23.14
				45072	116.5	118.0	1.5	2.7	2099	96	23.24
				45073	118.0	119.5	1.5	2.7	2206	102	24.28
				45074	119.5	121.0	1.5	2.8	2153	101	23.66
				45075	121.0	122.5	1.5	2.8	2069	98	23.08
				45076	122.5	124.0	1.5	2.8	2209	103	23.93
				45077	124.0	125.5	1.5	2.8	2275	108	24.36
				45078	125.5	127.0	1.5	2.8	2111	102	23.63
				45079	127.0	128.5	1.5	2.8	2077	100	23.25
				45080	128.5	130.0	1.5	2.8	2024	97	23.16
				45081	130.0	131.5	1.5	2.8	2135	107	24.22
				45082	131.5	133.0	1.5	2.8	2210-	108	24.29
				45083	133.0	134.5	1.5	2.6	2568	125	27.14
				45084	134.5	136.0	1.5	2.6	2248	111	25.05
				45085	136.0	137.5	1.5	2.6	222	108	24.65
				45086	137.5	139.0	1.5	2.6	2204	106	24.61
				45087	139.0	140.5	1.5	2.6	2249	108	24.75
				45088	140.5	142.0	1.5	2.6	2137	108	24.46
				45089	142.0	143.5	1.5	2.6	2194	110	24.40
				45090	143.5	145.0	1.5	2.6	2199	118	25.07
				45091	145.0	146.5	1.5	2.6	2092	111	24.20
				45092	146.5	148.0	1.5	2.6	2067	116	24.10
				45093	148.0	149.5	1.5	2.6	2222	113	24.39
				45094	149.5	151.0	1.5	2.6	2147	120	24.43
				45095	151.0	152.4	1.4	2.6	2147	114	24.13

END OF HOLE

DIAMOND DRILL HOLE RECORD

PROPERTY: RECORD RIDGE SOUTH

DDH RRS08-24

3

DIP AND AZIMUTH TESTS			CORE SIZE: NQ	TOTAL DEPTH: 154.3m	DATE STARTED: August 6, 2008
DEPTH	ANGLE	AZIMUTH	HOLE ANGLE: - 90°	HOLE AZIMUTH °	DATE FINISHED: August 12, 2008
154.3m	-88.0°	279.2°	SECTION:	COLLAR ELEVATION: 1498.2m	ANALYSIS BY: Assayers Canada
			GRID LOCATION: 275S/ 1375W	RECOVERY:	LOGGED BY: H.K. & C.P.
			UTM (NAD 83): 5432614N 434527E	CLAIM: Frank Sr. 3	CORE STORED AT: Midnight camp

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni %	Co ppm	Mg %
0	2.7		Casing								
2.7	5.8	100	SERPENTINITE Greenish-black, magnetic, calcite-healed fractures at random intervals, somewhat fragmented.	45096 45097	2.7 4.2	4.2 5.8	1.5 1.6	2.6 2.6	1909 2102	87 97	20.83 22.67
5.8	7.9	80	SERPENTINITE Greenish-black, magnetic, calcite-healed fractures at random intervals, highly fragmented to pulverize. Contains cobble/gravel sized fragments of monzodiorite in pulverized section from 5.9-6.05m	45098	5.8	7.9	2.1	2.63	1435	87	20.37
7.9	12.0	100	SERPENTINITE Dark greenish-black, mottled with white calc-talcy blebs, strongly magnetic, contains fractures healed with calc-talcy material at random intervals.	45099 45100 45101	7.9 9.4 10.9	9.4 10.9 12.0	1.5 1.5 1.1	2.63 2.63 2.63	2168 2143 2047	100 90 104	22.50 21.64 22.61
12.0	33.5	100	SERPENTINITE Homogeneously black, massive, strongly magnetic, contains "silver looking" flakes throughout, contains fractures healed with calc-talcy material at random intervals.	45102 45103 45104 45105 45106 45107 45108 45109 45110 45111 45112 45113 45114	12.0 13.5 15.0 16.5 18.0 19.5 21.0 22.5 22.5 24.0 25.5 27.0 28.5 30.0	13.5 15.0 16.5 18.0 19.5 21.0 22.5 24.0 25.5 27.0 28.5 30.0 31.5	1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5	2.63 2.63 2.63 2.63 2.63 2.63 2.63 2.63 2.63 2.63 2.63 2.63 2.63 2.63	2107 2383 2385 2200 2214 2193 2285 2306 2292 2118 2258 2214 2210	93 108 116 107 109 106 114 108 116 109 114 102 107	22.14 23.34 23.98 23.72 23.60 24.18 25.62 23.70 25.19 24.37 25.63 24.68 25.21

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni %	Co ppm	Mg %
				45115	31.5	33.5	2.0	2.63	2202	104	25.01
33.5	36.5	100	SERPENTINITE Homogeneously black, massive, strongly magnetic, contains “silver looking” flakes throughout, more fragmented than previous section with most fractures healed by light-green soapstone.	45116 45117	33.5 35.0	35.0 36.5	1.5 1.5	2.63 2.63	2213 2134	109 110	24.79 24.81
36.5	38.4	100	SERPENTINITE Homogeneously black, massive, strongly magnetic, contains “silver looking” flakes throughout, contains fractures healed with calc-talcy material at random intervals.	45118	36.5	38.4	1.9	2.63	2238	115	25.01
38.4	43.35	100	SERPENTINITE Dark greenish-black, mottled with white calc-talcy blebs, strongly magnetic, contains fractures healed with calc-talcy material at random intervals.	45119 45120 45121	38.4 39.9 41.4	39.9 41.4 43.35	1.5 1.5 1.95	2.63 2.63 2.63	2244 2321 2021	118 116 103	25.54 25.83 24.68
43.35	44.25	100	SERPENTINIZED ANDESITE Light grey, weakly magnetic, fractures throughout that are lined with serpentine. Both upper and lower contacts are sharp, 45° to c.a. and lined with soapstone.	45122	43.35	44.25	0.9	2.74	108	43	7.06
44.25	130.0	100	SERPENTINITE Homogeneously black, massive, strongly magnetic, contains “silver looking” flakes throughout, visually conspicuous silver looking mineral with cubic habit. Somewhat fragmented from 48.8-49.2m & 76.0-78.0m	45123 45124 45125 45126 45127 45128 45129 45130 45131 45132 45133 45134 45135 45136 45137 45138 45139 45140 45141 45142 45143 45144 45145	44.25 45.8 47.3 48.8 50.3 51.8 53.3 54.8 56.3 57.8 59.3 60.8 62.3 63.8 65.3 66.8 68.3 69.8 71.3 72.8 74.3 75.8 77.3 77.3	45.8 47.3 48.8 50.3 51.8 53.3 54.8 56.3 57.8 59.3 60.8 62.3 63.8 65.3 66.8 68.3 69.8 71.3 72.8 74.3 75.8 77.3 78.8	1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5	2.63 2.63 2.63 2.63 2.63 2.63 2.63 2.63 2.63 2.63 2.63 2.63 2.63 2.63 2.63 2.63 2.63 2.63 2.63 2.63 2.63 2.63 2.63	1862 2138 2167 2264 2258 2176 2200 2129 2124 2036 2221 2270 2216 2256 2261 2335 2342 2127 2200 2331 2306 2350 2080	96 112 111 111 118 118 114 111 106 106 112 107 116 108 108 111 112 102 105 109 114 123 102	23.37 24.27 24.31 24.71 24.76 23.62 23.48 24.24 24.24 23.74 24.73 24.56 25.24 24.74 25.58 26.06 24.02 24.39 24.06 24.52 25.02 24.05 23.78

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni %	Co ppm	Mg %
				45146	78.8	80.3	1.5	2.63	2198	108	24.01
				45147	80.3	81.8	1.5	2.63	2267	105	25.81
				45148	81.8	83.3	1.5	2.63	2169	109	24.41
				45149	83.3	84.8	1.5	2.63	2317	110	24.63
				45150	84.8	86.3	1.5	2.63	2130	103	24.15
				45151	86.3	87.8	1.5	2.63	2091	104	24.72
				45152	87.8	89.3	1.5	2.63	20833	100	24.49
				45153	89.3	90.8	1.5	2.63	2262	108	24.93
				45154	90.8	92.3	1.5	2.63	2214	101	23.83
				45155	92.3	93.8	1.5	2.63	2055	98	23.77
				45156	93.8	95.3	1.5	2.63	2216	106	25.40
				45157	95.3	96.8	1.5	2.63	1958	106	24.63
				45158	96.8	98.3	1.5	2.63	2348	111	25.18
				45159	98.3	99.8	1.5	2.63	2204	106	25.23
				45160	99.8	101.3	1.5	2.63	2282	105	24.51
				45161	101.3	102.8	1.5	2.63	2274	109	25.49
				45162	102.8	104.3	1.5	2.63	2328	113	24.49
				45163	104.3	105.8	1.5	2.63	2440	113	25.95
				45164	105.8	107.3	1.5	2.63	2261	110	24.66
				45165	107.3	108.8	1.5	2.63	2258	105	24.75
				45166	108.8	110.3	1.5	2.63	2173	104	24.37
				45167	110.3	111.8	1.5	2.63	2386	116	25.62
				45168	111.8	113.3	1.5	2.63	2389	115	25.39
				45169	113.3	114.8	1.5	2.63	2102	106	24.96
				45170	114.8	116.3	1.5	2.63	2419	113	26.66
				45171	116.3	117.8	1.5	2.63	2527	115	25.54
				45172	117.8	119.3	1.5	2.63	2296	115	25.87
				45173	119.3	120.8	1.5	2.63	1985	104	25.80
				45174	120.8	122.3	1.5	2.63	2282	117	25.18
				45175	122.3	123.8	1.5	2.63	2540	124	27.10
				45176	123.8	125.3	1.5	2.63	2265	110	25.39
				45177	125.3	126.8	1.5	2.63	2178	107	25.09
				45178	126.8	128.3	1.5	2.63	2178	107	24.50
				45179	128.3	130.0	1.5	2.63	2495	122	24.42
130.0	135.3	100	SERPENTINITE Black with silver flakes and white blebs of calc-talcy material, also contains a web of serpentine-lined fractures running throughout the section. Lower contact is sharp and 60° to c.a., the contact is also coated it light green-serpentine and heavily mineralized with pyrite and possibly chalcopyrite.	45180	130.0	131.5	1.5	2.68	2455	119	25.59
				45181	131.5	133.0	1.5	2.68	2130	103	22.85
				45182	133.0	134.2	1.2	2.68	1987	96	21.46
				45183	134.2	135.3	1.1	2.68	1796	89	15.91
135.3	154.25	100	MONZOSYENITE Euhedral to sub-euhedral feldspar phenocrysts up to 7mm, also biotite flecks up to 3mm long as well as hornblende phenocrysts up to 3mm,	45184	135.3	137.3	2.0	2.81	116	30	3.92
				45185	137.3	139.3	2.0	2.81	32	20	1.81
				45186	139.3	141.3	2.0	2.81	30	19	1.57
				45187	141.3	143.3	2.0	2.81	25	17	1.30

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni %	Co ppm	Mg %
			all set in a light-grey, medium-grained (with some pinkish hues) groundmass. Upper contact is sharp and 60° to c.a., the contact is also coated it light green-serpentine and heavily mineralized with pyrite and possibly chalcopyrite.	45188	143.3	145.3	2.0	2.81	21	15	1.02
				45189	145.3	147.3	2.0	2.81	22	15	1.07
				45190	147.3	149.3	2.0	2.81	19	14	0.88
				45191	149.3	151.3	2.0	2.81	20	15	1.00
				45192	151.3	153.3	1.7	2.81	20	14	0.99
			This section is identical in hand sample comparison to the rock found in RRS08-23 (21.0m and sample number 45009)	45193	153.3	154.25	1.25	2.81	28	19	1.52

END OF HOLE

DIAMOND DRILL HOLE RECORD

PROPERTY: RECORD RIDGE SOUTH

DDH RRS08-25

DIP AND AZIMUTH TESTS			CORE SIZE: NQ	TOTAL DEPTH: 123.8m	DATE STARTED; August 12, 2008
DEPTH	ANGLE	AZIMUTH	HOLE ANGLE: - 90°	HOLE AZIMUTH °	DATE FINISHED: August 19, 2008
123.8m	-88.0°	279.2°	SECTION:	COLLAR ELEVATION: 1506.0m	ANALYSIS BY: Assayers Canada
			GRID LOCATION: 203S/ 1382W	RECOVERY:	LOGGED BY: H.K. & C.P.
			UTM (NAD 83): 5432686N 434520E	CLAIM: Frank Sr. 3	CORE STORED AT: Midnight camp

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm³)	Ni %	Co ppm	Mg %
0	0.6		CASING								
0.6	11.6	100	SERPENTINITE Dark greenish-black, magnetic, somewhat fragmented, higher frequency of talcy-calc lined fractures from 8.8-11.7m	45276 45277 45278 45279 45280 45281 45282	0.6 2.1 3.6 5.1 6.6 8.1 9.6	2.1 3.6 5.1 6.6 8.1 9.6 11.6	1.5 1.5 1.5 1.5 1.5 1.5 2.0	2.68 2.68 2.68 2.68 2.68 2.68 2.68	2346 2082 1957 1941 2076 1924 1977	108 107 100 101 99 97 95	21.75 22.58 22.98 24.16 24.23 20.89 21.05
11.6	13.5	80	ANDESITE Highly fragmented to pulverized, greenish-grey, aphanitic, non-magnetic.	45283	11.6	13.5	1.9	2.68	53	32	5.0
13.5	15.85	80	ANDESITE/ DIORITE Rock is more like a regolith, has been almost completely broken down into soil-like state and weathered to a light brown dusty texture.	45284	13.5	15.85	2.35	n/a	121	41	3.9
15.85	20.1	100	ANDESITE Dark-grey, aphanitic, weakly magnetic, somewhat fragmented, contains sporadic white calcareous blebs.	45285 45286	15.85 18.0	18.0 20.1	2.15 2.1	2.75 2.75	28 22	35 37	3.3 2.9
20.1	24.15	100	DIAGABBRO Med.-coarse grained, dark grey, equigranular, fragmented with calcite-lined fractures.	45287 45288	20.1 22.1	22.1 24.15	2.0 2.05	2.78 2.78	12 13	35 27	2.6 2.5
24.15	27.65	100	ANDESITE Dark-grey, aphanitic, highly fragmented, weakly magnetic, somewhat fragmented, contains sporadic white calcareous blebs.	45289 45290	24.15 26.0	26.0 27.65	1.85 1.65	2.76 2.76	14 118	32 31	4.5 4.7
27.65	32.3	100	SERPENTINITE Dark green, magnetite stringers & blebs of white talcy material throughout, somewhat fragmented.	45291 45292 45293	27.65 29.2 30.7	29.2 30.7 32.3	1.55 1.5 1.6	2.68 2.68 2.68	1748 1926 1813	91 97 91	16.88 21.27 20.31

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni %	Co ppm	Mg %
32.3	72.55	100	SERPENTINITE Homogeneously black, magnetic, contains “silver-looking” flakes (2-5%)	45294	32.3	34.1	1.5	2.65	2209	118	24.64
				45295	34.1	35.6	1.5	2.65	2031	106	24.82
				45296	35.6	37.1	1.5	2.65	2136	110	23.89
				45297	37.1	38.6	1.5	2.65	2109	107	24.76
				45298	38.6	40.1	1.5	2.65	2243	108	24.65
				45299	40.1	41.6	1.5	2.65	2375	116	25.68
				45300	41.6	43.1	1.5	2.65	2194	110	25.14
				45301	43.1	44.6	1.5	2.65	2072	108	24.05
				45302	44.6	46.1	1.5	2.65	2125	101	24.14
				45303	46.1	47.6	1.5	2.65	2014	100	22.21
				45304	47.6	49.1	1.5	2.65	2044	103	23.89
				45305	49.1	50.6	1.5	2.65	2344	108	24.66
				45306	50.6	52.1	1.5	2.65	2228	105	24.24
				45307	52.1	53.6	1.5	2.65	2378	110	26.07
				45308	53.6	55.1	1.5	2.65	2149	105	24.47
				45309	55.1	56.6	1.5	2.65	2172	106	24.50
				45310	56.6	58.1	1.5	2.65	2171	106	24.42
				45311	58.1	59.6	1.5	2.65	2270	107	25.67
				45312	59.6	61.1	1.5	2.65	2314	111	25.46
				45313	61.1	62.6	1.5	2.65	2202	105	24.64
				45314	62.6	64.1	1.5	2.65	2280	100	25.14
				45315	64.1	65.6	1.5	2.65	2258	94	23.86
				45316	65.6	67.1	1.5	2.65	2109	101	24.70
				45317	67.1	68.6	1.5	2.65	2212	107	23.73
				45318	68.6	70.1	1.5	2.65	2070	102	23.63
				45319	70.1	71.6	1.5	2.65	2160	101	24.09
				45320	71.6	72.55	0.95	2.65	2013	97	23.63
72.55	75.2	100	SERPENTINITE Light-green soapstone with talcy-calcareous stringers and fractures throughout, magnetic.	45321	72.55	74.0	1.45	2.68	1671	84	17.84
				45322	74.0	75.2	1.2	2.68	1762	97	18.38
75.2	88.4	100	SERPENTINITE Homogeneously black, magnetic, contains “silver-looking” flakes (2-5%)	45323	75.2	76.7	1.5	2.65	2337	108	24.92
				45324	76.7	78.2	1.5	2.65	2200	108	24.66
				45325	78.2	79.7	1.5	2.65	2248	109	25.11
				45326	79.7	81.2	1.5	2.65	2272	113	24.74
				45327	81.2	82.7	1.5	2.65	2217	107	24.82
				45328	82.7	84.2	1.5	2.65	2215	111	24.79
				45329	84.2	85.7	1.5	2.65	2374	110	25.89
				45330	85.7	87.2	1.5	2.65	2449	119	25.19
				45331	87.2	88.4	1.2	2.65	2470	114	24.44
88.4	104.5	100	MONZOSYENITE Euhedral to sub-euhedral feldspar phenocrysts up to 7mm, also biotite flecks up to 3mm long set in a light-grey, medium-grained (with some pinkish hues) groundmass	45332	88.4	90.4	2.0	2.68	129	21	4.6
				45333	90.4	92.4	2.0	2.68	29	19	1.7
				45334	92.4	94.4	2.0	2.68	29	19	1.6
				45335	94.4	96.4	2.0	2.68	158	24	2.7
				45336	96.4	98.4	2.0	2.68	30	19	1.4
				45337	98.4	100.4	2.0	2.68	28	19	1.5

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni %	Co ppm	Mg %
				45338 45339	100.4 102.4	102.4 104.5	2.0 2.1	2.68 2.68	27 27	19 18	1.5 1.5
104.5	106.5	100	SERPENTINITE Dark greenish-black, fragmented, moderately magnetic, talcy-calcareous fractures throughout	45340	104.5	106.5	2.0	2.63	2304	106	25.54
106.5	123.8	100	SERPENTINITE Homogeneously black, magnetic, contains “silver-looking” flakes (2-5%). 116.17-116.53m is a white/ light-green soapstone section.	45341 45342 45343 45344 45345 45346 45347 45348 45349 45350 45351 45352	106.5 108.0 109.5 111.0 112.5 114.0 115.5 117.0 118.5 120.0 121.5 122.8	108.0 109.5 111.0 112.5 114.0 115.5 117.0 118.5 120.0 121.5 122.8	1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.3 1.0	2.65 2.65 2.65 2.65 2.65 2.65 2.65 2.65 2.65 2.70 2.70 2.70	2293 2284 2363 2438 2205 2248 2396 2200 2225 2396 2323 2213	107 106 110 113 104 106 109 107 105 109 107 105	25.11 25.34 25.86 26.10 24.45 24.44 26.14 25.52 25.06 25.60 25.76 25.54

END OF HOLE

DIAMOND DRILL HOLE RECORD

PROPERTY: RECORD RIDGE SOUTH

DDH RRS08-26

DIP AND AZIMUTH TESTS			CORE SIZE: NQ	TOTAL DEPTH: 123.8m	DATE STARTED; August 12, 2008
DEPTH	ANGLE	AZIMUTH	HOLE ANGLE: - 90°	HOLE AZIMUTH °	DATE FINISHED: August 14, 2008
104.9m	-89.2°	220.2°	SECTION:	COLLAR ELEVATION: 1503.8m	ANALYSIS BY: Assayers Canada
			GRID LOCATION: 250S/ 1375W	RECOVERY:	LOGGED BY: H.K. & C.P.
			UTM (NAD 83): 5432639N 434527E	CLAIM: Frank Sr. 3	CORE STORED AT: Midnight camp

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni %	Co ppm	Mg %
0	1.2		CASING								
1.2	5.45	100	SERPENTINITE Dark greenish-black, strongly magnetic, magnetic stringers throughout, relatively intact core.	45194 45195 45196	1.2 2.7 4.2	2.7 4.2 5.45	1.5 1.5 1.25	2.65 2.65 2.65	2286 2290 2302	111 108 113	24.0 23.45 24.16
5.45	14.5	80	SERPENTINITE Dark greenish-black, strongly magnetic, magnetic stringers throughout. Pulverized to highly fragmented throughout the section with some longer (up to 45cm) of intact serpentine core.	45197 45198 45199 45200 45201 45202	5.45 7.0 8.5 10.0 11.5 13.0	7.0 8.5 10.0 11.5 13.0 14.5	1.55 1.5 1.5 1.5 1.5 1.5	N/A N/A N/A N/A N/A N/A	1817 2917 1530 1021 888 2135	90 96 96 78 70 115	19.64 17.23 15.44 13.29 12.14 13.20
14.5	23.3	100	SERPENTINITE Dark greenish-grey, magnetic, covered in talcy-calcareous healed fractures, magnetite webs throughout.	45203 45204 45205 45206 45207 45208	14.5 16.0 17.5 19.0 20.5 22.0	16.0 17.5 19.0 20.5 22.0 23.3	1.5 1.5 1.5 1.5 1.5 1.3	2.8 2.8 2.8 2.8 2.8 2.8	1709 2123 2167 2066 1968 1958	93 108 104 102 110 104	19.67 21.12 21.87 22.23 22.96 22.81
23.3	60.05	100	SERPENTINITE Homogeneously black, strongly magnetic, “silver-looking” flakes throughout (2-4%).	45209 45210 45211 45212 45213 45214 45215 45216 45217 45218 45219 45220 45221	23.3 24.8 26.3 27.8 29.3 30.8 32.3 33.8 35.3 36.8 38.3 39.8 41.3	24.8 26.3 27.8 29.3 30.8 32.3 33.8 35.3 36.8 38.3 39.8 41.3 42.8	1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5	2.65 2.65 2.65 2.65 2.65 2.65 2.65 2.65 2.65 2.65 2.65 2.65 2.65	2364 2284 2203 2332 2196 2092 2549 2287 2335 2426 2187 2178 2268	117 114 108 111 113 115 121 114 108 109 108 97 101	24.73 24.49 23.33 24.58 24.43 24.82 26.95 24.98 25.65 24.83 24.47 23.73 24.04

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni %	Co ppm	Mg %
				45222	42.8	44.3	1.5	2.65	2354	101	24.87
				45223	44.3	45.8	1.5	2.65	2151	95	23.74
				45224	45.8	47.3	1.5	2.65	2101	90	23.53
				45225	47.3	48.8	1.5	2.65	2134	100	24.42
				45226	48.8	50.3	1.5	2.65	2288	108	24.99
				45227	50.3	51.8	1.5	2.65	2328	109	25.31
				45228	51.8	53.3	1.5	2.65	2230	107	24.21
				45229	53.3	54.8	1.5	2.65	2289	112	25.24
				45230	54.8	56.3	1.5	2.65	2260	104	24.00
				45231	56.3	57.8	1.5	2.65	2200	109	23.52
				45232	57.8	59.0	1.2	2.65	2001	99	22.06
				45233	59.0	60.05	1.05	2.65	2061	100	20.90
60.05	61.25	100	SERPENTINIZED ANDESITE Grey, magnetic, covered in web of talcy-calcareous filled fractures throughout.	45234	60.05	61.25	1.2	2.76	45	47	13.59
61.25	67.15	100	SERPENTINITE Black, magnetic, has a silver sheen to it due to the increased abundance (up to 15% of rock) of the “silver-looking” flakes seen in the previous section.	45235	61.25	62.8	1.55	2.68	2225	106	22.23
				45236	62.8	64.3	1.5	2.68	2138	105	23.16
				45237	64.3	65.8	1.5	2.68	2123	104	22.81
				45238	65.8	67.15	1.5	2.68	2045	105	23.32
67.15	75.75	100	SERPENTINITE Homogeneously black, strongly magnetic, “silver-looking” flakes throughout (2-4%).	45239	67.15	68.7	1.55	2.65	2247	106	23.87
				45240	68.7	70.2	1.5	2.65	2091	102	22.35
				45241	70.2	71.7	1.5	2.65	1925	100	22.44
				45242	71.7	73.2	1.5	2.65	2158	103	22.47
				45243	73.2	74.5	1.3	2.65	2102	107	22.89
				45244	74.5	75.75	1.25	2.65	2112	101	22.45
75.75	77.0	100	SERPENTINE Green, fragmented, fractured throughout, weakly to non-magnetic.	45245	75.75	77.0	1.25	2.76	1721	75	19.94
77.0	105.8	100	SERPENTINITE Black, magnetic, littered with “silver looking” flakes (2-5%). Magnetic webbing throughout. Lower contact is serpentine, soft and 45° c.a. Serpentine section similar to 75.75-77.0m but less fragmented from 90.1-90.4m.	45246	77.0	78.5	1.5	2.65	2094	108	24.41
				45247	78.5	80.0	1.5	2.65	2222	110	24.32
				45248	80.0	81.5	1.5	2.65	2191	111	24.72
				45249	81.5	83.0	1.5	2.65	2125	109	24.90
				45250	83.0	84.5	1.5	2.65	2215	112	25.37
				45251	84.5	86.0	1.5	2.65	2302	112	25.32
				45252	86.0	87.5	1.5	2.65	2070	112	24.72
				45253	87.5	89.0	1.5	2.65	2084	111	24.20
				45254	89.0	90.5	1.5	2.65	1952	93	22.51
				45255	90.5	92.0	1.5	2.65	2152	113	23.92
				45256	92.0	93.5	1.5	2.65	1968	105	22.37
				45257	93.5	95.0	1.5	2.65	2068	105	24.36
				45258	95.0	96.5	1.5	2.65	2214	116	25.92
				45259	96.5	98.0	1.5	2.65	2095	106	24.41
				45260	98.0	99.5	1.5	2.65	2030	105	24.23
				45261	99.5	101.0	1.5	2.65	2098	107	24.37

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni %	Co ppm	Mg %
				45262	101.0	102.5	1.5	2.65	2275	115	25.45
				45263	102.5	104.0	1.5	2.65	2283	118	26.16
				45264	104.0	105.8	1.8	2.65	2070	103	23.92
105.8	108.25	100	DIORITE Medium-coarse grained, greenish-grey, non-magnetic, mafic phenocrysts (3mm), biotite flecks, calcareous lined fractured throughout. Upper and lower contacts are 45° to c.a. and sharp.	45265	105.8	108.25	2.45	2.70	74	39	4.82
108.25	123.8	100	SERPENTINITE Black, magnetic, littered with “silver looking” flakes (2-5%). Magnetic webbing throughout.	45266	108.25	109.8	1.55	2.65	2035	104	23.40
				45267	109.8	111.3	1.5	2.65	2059	106	23.77
				45268	111.3	112.8	1.5	2.65	2057	109	24.00
				45269	112.8	114.3	1.5	2.65	2110	107	23.93
				45270	114.3	115.8	1.5	2.65	2122	107	23.92
				45271	115.8	117.3	1.5	2.65	2101	110	24.49
				45272	117.3	118.8	1.5	2.65	2068	112	24.47
				45273	118.8	120.3	1.5	2.65	2102	106	24.49
				45274	120.3	121.8	1.5	2.65	2116	104	24.10
				45275	121.8	123.8	2.0	2.65	2126	108	22.66

END OF HOLE

DIAMOND DRILL HOLE RECORD

PROPERTY: RECORD RIDGE SOUTH

DDH RRS08-27

DIP AND AZIMUTH TESTS			CORE SIZE: NQ	TOTAL DEPTH: 123.8m	DATE STARTED: August 14, 2008
DEPTH	ANGLE	AZIMUTH	HOLE ANGLE: - 90°	HOLE AZIMUTH °	DATE FINISHED: August 21, 2008
	°	000°	SECTION:	COLLAR ELEVATION: 1496.1m	ANALYSIS BY: Assayers Canada
			GRID LOCATION: 300S/ 1375W	RECOVERY:	LOGGED BY: H.K. & C.P.
			UTM (NAD 83): 5432589N 434527E	CLAIM: Frank Sr. 3	CORE STORED AT: Midnight camp

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni %	Co ppm	Mg %
0	1.0		CASING								
1.0	5.3	100	SERPENTINITE Dark grayish-green, white talcy-calcareous blebs, moderately magnetic, fragmented, with fractures that are rusted and lined with talcy-calcareous material.	45354 45355 45356	1.0 2.5 4.0	2.5 4.0 5.3	1.5 1.5 1.3	2.7 2.7 2.7	2302 2235 2160	113 110 106	24.08 24.67 24.54
5.3	13.6	100	SERPENTINITE Less fragmented than previous section, dark grayish-green, white talcy-calcareous blebs, moderately magnetic, fractures that are lined with talcy-calcareous material.	45357 45358 45359 45360 45361 45362	5.3 6.8 8.3 9.8 11.3 12.5	6.8 8.3 9.8 11.3 12.5 13.6	1.5 1.5 1.5 1.5 1.5 1.1	2.7 2.7 2.7 2.7 2.7 2.7	2488 2147 2365 2147 2287 2188	117 103 112 110 110 107	26.43 23.71 24.98 25.55 25.38 24.09
13.6	48.5	100	SERPENTINITE Homogeneously black, magnetic, magnetite webs throughout, some sporadic white talcy-calcareous blebs and "silver-looking" flakes throughout (<2%).	45363 45364 45365 45366 45367 45368 45369 45370 45371 45372 45373 45374 45375 45376 45377 45378 45379 45380	13.6 15.1 16.6 18.1 19.6 21.1 22.6 24.1 25.6 27.1 28.6 30.1 31.6 33.1 34.6 36.1 37.6 39.1	15.1 16.6 18.1 19.6 21.1 22.6 24.1 25.6 27.1 28.6 30.1 31.6 33.1 34.6 36.1 37.6 40.6	1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5	2.7 2.7 2.7 2.7 2.7 2.65 2.65 2.65 2.65 2.65 2.65 2.65 2.65 2.65 2.65 2.65 2.65	2368 2337 2295 2355 2159 2295 2325 2352 2308 2088 2169 2153 2200 1008 1770 1969 2065 2129	119 112 114 120 106 110 116 115 112 110 108 114 114 103 107 105 89	25.96 25.69 25.71 26.87 24.52 25.41 25.70 25.27 25.40 24.75 25.22 25.35 26.38 25.11 22.93 23.91 24.54 25.41

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni %	Co ppm	Mg %
				45381	40.6	42.1	1.5	2.8	1886	85	21.65
				45382	42.1	43.6	1.5	2.8	2088	81	22.48
				45383	43.6	45.1	1.5	2.8	1888	88	21.19
				45384	45.1	46.6	1.5	2.8	1704	65	19.57
				45385	46.6	48.5	1.5	2.8	1575	62	19.21
48.5	50.4	100	SERPENTINITE Homogeneously black but magnetic, high frequency of soapstone-lined fractures running across the section at 70° to the c.a.	45386	48.5	50.4	1.9	2.7	1570	92	22.49
50.4	63.5	100	SERPENTINITE Homogeneously black, magnetic, magnetite webs throughout, some sporadic white talcy-calcareous blebs and “silver-looking” flakes throughout (<2%).	45387	50.4	51.9	1.5	2.8	2048	92	24.00
				45388	51.9	53.4	1.5	2.8	2094	110	26.15
				45389	53.4	54.9	1.5	2.8	2121	110	25.62
				45390	54.9	56.4	1.5	2.8	2037	113	25.24
				45391	56.4	57.9	1.5	2.8	2125	121	25.86
				45392	57.9	59.4	1.5	2.8	1874	112	24.68
				45393	59.4	60.9	1.5	2.8	1548	108	24.40
				45394	60.9	62.4	1.5	2.8	1382	101	24.71
				45395	62.4	63.5	1.5	2.8	1756	108	23.72
63.5	65.8	100	DIAGABBRO Med.-coarse grained, dark grey, mafic phenocrysts 2-3mm (hbl or px) as well as biotite flakes 1-2mm. Core is somewhat fragmented and both upper and lower contacts are 40° to the c.a.	45396	63.5	65.8	2.0	2.76	152	26	3.0
65.8	67.4	100	SERPENTINITE Dark greenish-grey, magnetite webs, solid, magnetic.	45397	65.8	67.4	1.6	2.71	1940	104	23.33
67.4	69.0	100	SERPENTINE Fragmented, soft, grey with light-green soapstone throughout.	45398	67.4	69.0	1.6	2.76	1546	90	18.11
69.0	70.8	100	SERPENTINITE Homogeneously black, magnetic, magnetite webs throughout, some sporadic white talcy-calcareous blebs and “silver-looking” flakes throughout (<2%).	45399	69.0	70.8	1.8	2.70	1967	112	23.93
70.8	72.8	100	ANDESITE Greenish-grey, fragmented to pulverized, non-magnetic, lower contact is pulverized.	45400	70.8	72.8	2.0	2.42	193	44	5.95
72.8	123.8	100	SERPENTINITE Homogeneously black, magnetic, magnetite webs throughout, some sporadic white talcy-calcareous blebs and “silver-looking” flakes throughout (<2%).	45401	72.8	74.3	1.5	2.63	2242	116	25.54
				45402	74.3	75.8	1.5	2.63	2308	112	25.81
				45403	75.8	77.3	1.5	2.63	2333	110	25.78
				45404	77.3	78.8	1.5	2.63	2243	109	25.06
				45405	78.8	80.3	1.5	2.63	2321	109	24.11
				45406	80.3	81.8	1.5	2.63	2301	110	25.07
				45407	81.8	83.3	1.5	2.63	2247	107	24.59

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni %	Co ppm	Mg %
				45408	83.3	84.8	1.5	2.63	2306	108	25.01
				45409	84.8	86.3	1.5	2.63	2275	106	24.53
				45410	86.3	87.8	1.5	2.63	2321	109	23.26
				45411	87.8	89.3	1.5	2.63	2153	109	26.11
				45412	89.3	90.8	1.5	2.63	2283	109	25.25
				45413	90.8	92.3	1.5	2.63	2387	112	24.92
				45414	92.3	93.8	1.5	2.63	2409	115	26.29
				45415	93.8	95.3	1.5	2.63	2329	109	26.33
				45416	95.3	96.8	1.5	2.63	2481	110	26.47
				45417	96.8	98.3	1.5	2.63	2467	107	26.11
				45418	98.3	99.8	1.5	2.68	2555	110	25.68
				45419	99.8	101.3	1.5	2.68	2426	109	24.84
				45420	101.3	102.8	1.5	2.68	2349	109	26.83
				45421	102.8	104.3	1.5	2.68	2482	105	26.12
				45422	104.3	105.8	1.5	2.68	2429	102	26.36
				45423	105.8	107.3	1.5	2.68	2275	97	24.88
				45424	107.3	108.8	1.5	2.68	2311	97	24.82
				45425	108.8	110.3	1.5	2.68	2314	98	25.55
				45426	110.3	111.8	1.5	2.82	2446	103	26.25
				45427	111.8	113.3	1.5	2.82	2414	106	27.12
				45428	113.3	114.8	1.5	2.82	2434	102	26.90
				45429	114.8	116.3	1.5	2.82	2415	100	26.99
				45430	116.3	117.8	1.5	2.82	26242	101	27.93
				45431	117.8	119.3	1.5	2.82	389	100	26.70
				45432	119.3	120.8	1.5	2.82	2415	101	25.82
				45433	120.8	122.3	1.5	2.82	2347	99	25.48
				45434	122.3	123.8	1.5	2.82	2229	92	24.71

END OF HOLE

DIAMOND DRILL HOLE RECORD

PROPERTY: RECORD RIDGE SOUTH

DDH RRS08-28

DIP AND AZIMUTH TESTS			CORE SIZE: NQ	TOTAL DEPTH: 75m	DATE STARTED: August 26, 2008
DEPTH	ANGLE	AZIMUTH	HOLE ANGLE: - 90°	HOLE AZIMUTH °	DATE FINISHED: August 28, 2008
75m	-89.9°	117.6°	SECTION:	COLLAR ELEVATION: 1514.3m	ANALYSIS BY: Assayers Canada
			GRID LOCATION: 1425W/ 275S	RECOVERY:	LOGGED BY: H.K. & C.P.
			UTM (NAD 83) : 5432614N 434477E	CLAIM: Frank Sr. 3	CORE STORED AT: Midnight camp

Note: Only selectively assayed for Chromium and nickel sulfide

DEPTH (meters) FROM TO		Recovery (%)	Description	Sample No.	From (m)	To (m)	Length (m)	P (g/cm³)	Ni (%)	Co (ppm)	Mg (%)	Cr (%)	NiS ppm
			Casing to 0.9 m										
0	3.3	75	SERPENTINITE Milky white; moderately fragmented; weak to moderately magnetic	45671 45672	0 1.6	1.6 3.3	1.6 1.7	2.7 2.64	2277 2485	112 115	22.71 25.47		
3.3	23.9	100	SERPENTINITE Homogeneously black with magnetite webbing	45673 45674 45675 45676 45677 45678 45679 45680 45681 45682 45683 45684 45685 45686	3.3 4.8 6.3 7.8 9.3 10.8 12.3 13.8 15.3 16.8 18.3 19.8 21.3 22.8	4.8 6.3 7.8 9.3 10.8 12.3 13.8 15.3 16.8 18.3 19.8 21.3 22.8	1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5	2.67 2.67 2.75 2.75 2.75 2.63 2.63 2.63 2.63 2.60 260 2.60 2.55 2.55	2379 2102 2412 2435 2416 2340 2392 2335 2457 2206 2419 2534 2338 2388	112 111 113 121 124 111 116 115 109 113 110 121 113 116	24.60 25.04 25.71 25.73 25.68 25.01 25.23 26.12 25.55 25.35 25.39 25.14 25.10 24.94		
23.9	24.3	100	TALC VEIN White steatite; both contacts 30° to c.a.	45687	23.9	24.3	0.4	2.44	1783	119	23.19		
24.3	34.2	100	SERPENTINITE Homogeneously black with magnetite webbing	45688 45689 45690 45691 45692 45693 45694	24.3 25.8 27.3 28.8 30.3 31.8 33.3	25.8 27.3 28.8 30.3 31.8 33.3 34.2	1.5 1.5 1.5 1.5 1.5 1.5 0.9	2.65 2.65 2.65 2.65 2.65 2.65 2.65	2386 2264 2101 2126 2208 2102 2091	127 138 132 138 140 113 118	25.49 26.51 24.14 24.69 26.97 23.74 23.50	0.30 0.24 0.22 0.30 0.38 0.39	1296 795 1063 1206 1239 1157

DEPTH (meters) FROM TO		Recovery (%)	Description	Sample No.	From (m)	To (m)	Length (m)	P (g/cm ³)	Ni (%)	Co (ppm)	Mg (%)	Cr (%)	NiS ppm
34.2	40.0	100	SERPENTINITE	45695	34.2	35.7	1.5	2.60	2087	114	24.62	0.24	1399
			Moderately listwanized; dzrk grey to	45696	35.7	37.2	1.5	2.60	2110	119	24.33	0.50	1139
			black with calcite veinlets 20° to c.a and ;	45697	37.2	38.7	1.5	2.60	1754	88	22.38	0.20	791
			close spaced calc-talcose webbs	45698	38.7	40.0	1.3	2.60	2031	117	19.68	0.22	835
40.0	41.4	1.4	SERPENTINIZED ANDESIT Aphanitic; non-magnetic green to dark green	45699	40.0	41.4	1.4	2.71	578	57	10.57	0.21	95
41.4	75.0	100	QUARTZ SEYNITE TO	45700	41.4	43.0	1.6	2.55	76	37	4.86		
			MONZOSYENITE	45701	43.0	45.0	2	2.56	43	16	2.6		
			Euhedral feldspar phenos 3- 5 mm and	45702	45.0	47.0	2	2.60	37	21	2.4		
			mafics(biotite and hornblende) in a	45703	47.0	49.0	2	2.60	33	20	2.3		
			coarse grained light pinkish grey	45704	49.0	51.0	2	2.60	32	20	2.0		
			groundmass	45705	51.0	53.0	2	2.69	34	19	2.0		
				45706	53.0	55.0	2	2.69	30	18	2.0		
			End of Hole	45707	55.0	57.0	2	2.69	33	18	2.7		
				45708	57.0	59.0	2	2.54	29	18	1.9		
				45709	59.0	61.0	2	2.54	32	20	2.0		
				45710	61.0	63.0	2	2.67	31	20	1.9		
				45711	63.0	65.0	2	2.67	32	19	2.0		
				45712	65.0	67.0	2	2.55	35	20	2.0		
				45713	67.0	69.0	2	2.55	30	21	1.8		
				45714	69.0	71.0	2	2.55	32	22	2.0		
				45715	71.0	73.0	2	2.53	29	20	1.7		
				45716	73.0	75.0	2	2.53	29	20	1.8		

END OF HOLE

DIAMOND DRILL HOLE RECORD

PROPERTY: RECORD RIDGE SOUTH

DDH RRS08-29

DIP AND AZIMUTH TESTS			CORE SIZE: NQ	TOTAL DEPTH: 123.7m	DATE STARTED: August 21, 2008
DEPTH	ANGLE	AZIMUTH	HOLE ANGLE: - 90°	HOLE AZIMUTH °	DATE FINISHED:
123.7m	-89.9°	220.2°	SECTION:	COLLAR ELEVATION: 1500.0m	ANALYSIS BY: Assayers Canada
			GRID LOCATION: 1425 W / 328S	RECOVERY:	LOGGED BY: H.K. & C.P.
			UTM (NAD 83): 5432561N 434477E	CLAIM: Frank Sr. 3	CORE STORED AT: Midnight camp

DEPTH (meters) FROM TO		Recovery (%)	Description	Sample No.	From (m)	To (m)	Length (m)	P (g/cm ³)	Ni (%)	Co (ppm)	Mg (%)
			Casing to 3.4 m								
0	8.8	60	FRAGMENTED SERPENTINITE Light greenish dark grey; highly fragmented; limono-hematized; 50 % of the cores are soft green serpentine 4.6- 5.3 : green serpentine, soft pulverized	45510 45511 45512 45513 45514 45515	0 1.5 3.1 4.4 5.3 6.8	1.5 3.1 4.4 5.3 6.8 8.8	1.5 1.6 1.3 0.9 1.5 2	2.64 2.64 2.64 2.65 2.65 2.65	1814 2239 648 87 1583 334	80 91 67 49 85 59	20.44 22.38 14.29 16.22 21.28 12.31
8.8	26.3	100	SERPENTINITE Generally homogeneously black, solid and intact without tacl-calcareous webbing	45516 45517 45518 45519 45520 45521 45522 45523 45524 45525 45526 45527	8.8 10.3 11.8 13.3 14.8 16.3 17.8 19.3 20.8 22.3 22.8 25.3	10.3 11.8 13.3 14.8 16.3 17.8 19.3 20.8 22.3 22.8 25.3 26.3	1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1	2.68 2.68 2.68 2.68 2.68 2.68 2.64 2.64 2.64 2.64 2.64 2.64	2048 2221 2336 2291 2306 2208 2246 2162 2309 2358 2284 1888	102 107 109 107 108 105 110 109 112 110 111 91	23.78 23.71 24.65 24.22 23.96 24.54 23.12 24.41 25.10 25.58 24.55 20.18
26.3	28.8	100	SERPENTINIZED ANDESITE Light green; aphanitic and weakly magnetic; Both contacts broken and strongly serpentinized, but assumed to be 45° to c.a.	45528	26.3	28.8	2.5	2.76	283	57	7.22
28.8	60.3	100	SERPENTINITE Generally homogeneously black, solid and intact without tacl-calcareous webbing	45529 45530 45531 45532 45533	28.8 30.3 31.8 33.3 34.8	30.3 31.8 33.3 34.8 36.3	1.5 1.5 1.5 1.5 1.5	2.65 2.65 2.65 2.65 2.65	2002 2257 2287 2281 2202	103 113 105 110 108	21.78 25.05 25.33 26.03 24.51

DEPTH (meters) FROM TO		Recovery (%)	Description	Sample No.	From (m)	To (m)	Length (m)	P (g/cm ³)	Ni (%)	Co (ppm)	Mg (%)
				45534	36.3	37.8	1.5	2.65	2169	106	24.37
				45535	37.8	39.3	1.5	2.65	2375	110	25.49
				45536	39.3	40.8	1.5	2.65	2290	105	24.74
				45537	40.8	42.3	1.5	2.66	2363	112	25.31
				45538	42.3	43.8	1.5	2.66	2185	105	24.70
				45539	43.8	45.3	1.5	2.63	2211	103	24.37
				45540	45.3	46.8	1.5	2.63	2164	103	24.38
				45541	46.8	48.3	1.5	2.63	2280	109	25.08
				45542	48.3	49.8	1.5	2.66	2264	106	25.06
				45543	49.8	51.3	1.5	2.66	2164	107	24.36
				45544	51.3	52.8	1.5	2.66	2496	118	26.24
				45545	52.8	54.3	1.5	2.66	2082	106	23.53
				45546	54.3	55.8	1.5	2.66	2200	106	23.74
				45547	55.8	57.3	1.5	2.63	2206	108	23.49
				45548	57.3	58.8	1.5	2.63	2107	118	20.23
				45549	58.8	60.3	1.5	2.66	2101	105	23.07
60.3	61.5	100	SERPENTINITE Light Grey to dark grey; thinly banded calcite veinlets with calc-talcy webbing; moderately magnetic; green soft serpentine at random intervals	45550	60.3	61.5	1.2	2.76	1761	85	16.63
61.5	69.4	100	SERPENTINITE Homogeneously black without calc-talcoase webbing; lower contact shows a positive intrusive features and filled by green soft steatite 25° to c.a.	45551	61.5	63.0	1.5	2.68	1920	101	21.58
				45552	63.0	64.5	1.5	2.68	2063	104	22.70
				45553	64.5	66.0	1.5	2.62	2004	96	22.19
				45554	66.0	67.5	1.5	2.62	2107	105	23.75
				45555	67.5	69.4	1.9	2.50	2240	107	22.36
69.4	70.7	100	DIAGABBRO Medium grained; moderately fragmented	45556	69.4	70.7	1.3	2.65	97	25	4.00
70.7	72.6	100	SERPENTINIZED ANDESITE TO DIAGABBRO Dark green ; non to weakly magnetic; Lower 0.4 m section is totally pulverized in soft green serpentine(problem in drilling)	45557	70.7	72.6	1.9	2.57	1449	80	15.26
72.6	74.5	100	BASALTIC ANDESITE TO DIAGABBRO Also weakly serpentinized	45558	72.6	74.5	1.9	2.72	74	23	4.62
474.5	117.9	100	SERPENTINITE Black without calc-talcoase webbing; lower contact is sharp 40° to c.a.	45559	74.5	76.0	1.5	2.56	1754	91	19.95
				45560	76.0	77.5	1.5	2.53	2121	103	23.59
				45561	77.5	79.0	1.5	2.58	2224	108	24.24
				45562	79.0	80.5	1.5	2.58	2232	100	24.01
				45563	80.5	82.0	1.5	2.57	2175	101	23.86

DEPTH (meters) FROM TO		Recovery (%)	Description	Sample No.	From (m)	To (m)	Length (m)	P (g/cm ³)	Ni (%)	Co (ppm)	Mg (%)
				45564	82.0	83.5	1.5	2.69	2230	103	23.68
				45565	83.5	85.0	1.5	2.60	2174	103	23.94
				45566	85.0	86.5	1.5	2.60	2200	104	24.12
				45567	86.5	88.0	1.5	2.60	2084	98	23.10
				45568	88.0	89.5	1.5	2.61	2139	100	23.50
				45569	89.5	91.0	1.5	2.61	2228	106	23.89
				45570	91.0	92.5	1.5	2.61	2135	103	23.52
				45571	92.5	94.0	1.5	2.61	2073	102	23.17
				45572	94.0	95.5	1.5	2.61	2167	101	23.75
				45573	95.5	97.0	1.5	2.63	2034	84	20.88
				45574	97.0	98.5	1.5	2.63	1943	64	19.61
				45575	98.5	100.0	1.5	2.63	2296	85	22.65
				45576	100.0	101.5	1.5	2.63	1049	73	12.65
				45577	101.5	103.0	1.5	2.63	2155	100	23.22
				45578	103.0	104.5	1.5	2.63	2229	106	22.45
				45579	104.5	106.0	1.5	2.63	2084	98	22.47
				45580	106.0	107.5	1.5	2.63	2085	103	23.22
				45581	107.5	109.0	1.5	2.63	2162	110	23.63
				45582	109.0	110.5	1.5	2.54	2184	104	23.71
				45583	110.5	112.0	1.5	2.55	2268	113	24.27
				45584	112.0	113.5	1.5	2.55	2166	105	23.72
				45585	113.5	115.0	1.5	2.55	2241	108	24.46
				45586	115.0	116.5	1.5	2.55	2151	104	22.33
				45587	116.5	117.9	1.4	2.55	2046	101	22.47
117.9	123.7	100	MONZOSYENITE	45588	117.9	119.9	2	2.61	36	21	2.3
			Euhedral to sub-euhedral feldspar	45589	119.9	121.9	2	2.74	41	25	1.7
			phenos, 2 – 3 mm and mafics(hornblende	45590	121.9	123.7	1.8	2.64	34	24	1.6
			and/or biotite in a medium to coarse								
			graine light pinkish grey groundmass.								

END OF HOLE

DIAMOND DRILL HOLE RECORD

PROPERTY: RECORD RIDGE SOUTH

DDH RRS08-30

DIP AND AZIMUTH TESTS			CORE SIZE: NQ	TOTAL DEPTH: 124.6 m	DATE STARTED: August 25, 2008
DEPTH	ANGLE	AZIMUTH	HOLE ANGLE: - 90°	HOLE AZIMUTH °	DATE FINISHED: August 28, 2008
124.6	-87.8°	013.2°	SECTION:	COLLAR ELEVATION: 1514.7m	ANALYSIS BY: Assayers Canada
			GRID LOCATION:1425W / 222S	RECOVERY:	LOGGED BY: H.K. & C.P.
			UTM (NAD 83): 5432667N 434477E	CLAIM: Frank Sr. 3	CORE STORED AT: Midnight camp

Note: Selectively assayed for chromium and nickel sulfide

DEPTH (meters) FROM TO	Recovery (%)	Description	Sample No.	From (m)	To (m)	Length (m)	P (g/cm ³)	Ni (%)	Co (ppm)	Mg (%)	Cr (%)	NiS ppm
		Casing to 2.1m										
0	0.4	100	FRAGMENTED SERPENTINITE Dark grey serpentinite with magnetite webbing; included in sample 44591									
0.4	0.5	90	FAULT GOUGE in black rusted serpentinite Included in sample 44591									
0.5	3.9	30	FRAGMENTED SERPENTINIE Faulted and sheared zone in dark grey to black rusted serpentinite	45591	0	3.9	3.9	2.52	2502	118	19.46	
3.9	5.6	90	SERPENTINITE Dark grey to black, moderately fragmented	45592	3.9	5.6	1.7	2.52	1898	99	20.10	
5.6	5.7	100	FAULT GOUGE Included in sample 45593									
5.7	7.0	75	FRAGMENTED SERPENTINE Faulted, sheared and rusted zone similar to the previous section	45593	5.6	7.0	1.4	2.51	2157	105	22.18	
7.0	40.0	100	SERPENTINITE Homogeneously black, solid and intact with visible magnetite webs at close intervals	45594 45595 45596 45597 45598 45599 45600 45601	7.0 8.5 10.0 11.5 13.0 14.5 16.0 17.5	8.5 10.0 11.5 13.0 14.5 16.0 17.5 19.0	1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5	2.74 2.74 2.74 2.74 2.74 2.74 2.74 2.60	1977 2171 2092 2001 2383 2346 2409 2458	99 108 101 104 119 117 120 120	20.04 22.48 22.90 22.64 25.07 25.97 25.49 26.07	

DEPTH (meters) FROM TO		Recov ery (%)	Description	Sample No.	From (m)	To (m)	Length (m)	P (g/cm ³)	Ni (%)	Co (ppm)	Mg (%)	Cr (%)	NiS ppm
				45602	19.0	20.5	1.5	2.60	2330	113	25.21		
				45603	20.5	22.0	1.5	2.60	2291	108	24.59		
				45604	22.0	23.5	1.5	2.60	2240	113	24.32		
				45605	23.5	26.0	1.5	2.60	2233	106	23.53		
				45606	26.0	26.5	1.5	2.78	2180	100	22.28		
				45607	26.5	28.0	1.5	2.78	1532	89	19.32		
				45608	28.0	29.5	1.5	2.78	2207	106	23.69		
				45609	29.5	31.0	1.5	2.60	2090	101	22.98		
				45610	31.0	32.5	1.5	2.60	2282	113	23.81		
				45611	32.5	34.0	1.5	2.60	2261	110	23.61		
				45612	34.0	35.5	1.5	2.50	2204	114	23.79		
				45613	35.5	37.0	1.5	2.50	2217	106	24.21		
				45614	37.0	38.5	1.5	2.50	2142	104	22.83		
				45615	38.5	40.0	1.5	2.50	1984	100	20.47		
40.0	47.8	100	MONZOGABBRO TO MONZOSYENITE Coarse grained, euhedral phenos 2- 3 mm and mafics(biotite or hornblende) in a coarse grained light grey to pinkish grey groundmass	45616	40.0	42.0	2	2.58	53	25	2.90		
				44617	42.0	44.0	2	2.58	40	24	2.98		
				44618	44.0	46.0	2	2.61	42	26	2.45		
				44619	46.0	47.8	1.8	2.61	32	25	2.41		
47.8	124.6	100	SERPENTINITE Homogeneously black same as previously	45620	47.8	49.3	1.5	2.55	2112	107	23.01		
				45621	49.3	50.8	1.5	2.55	2287	112	25.12		
				45622	50.8	52.5	1.5	2.55	2405	113	25.26		
				45623	52.5	53.8	1.5	2.71	2130	108	23.90		
				45624	53.8	55.3	1.5	2.71	2438	113	25.02		
				45625	55.3	56.8	1.5	2.71	2050	98	22.04		
				45626	56.8	58.3	1.5	2.69	2279	111	24.66		
				45627	58.3	59.8	1.5	2.69	2298	110	24.39		
				45628	59.8	61.3	1.5	2.69	2605	124	26.31		
				45629	61.3	62.8	1.5	2.62	2492	119	26.47		
				45630	62.8	64.3	1.5	2.62	3123	151	33.81		
				45631	64.3	65.8	1.5	2.67	3134	150	33.90		
				45632	65.8	67.3	1.5	2.67	2417	120	25.51		
				45633	67.3	68.8	1.5	2.62	2373	112	25.74		
				45634	68.8	70.3	1.5	2.62	2434	117	25.59		
				45635	70.3	71.8	1.5	2.62	2425	118	25.56		
				45636	71.8	73.3	1.5	2.68	2280	113	25.47		
				45637	73.3	74.8	1.5	2.68	2446	118	25.90		
				45638	74.8	76.3	1.5	2.68	2385	118	26.41		
				45639	76.3	77.8	1.5	2.68	2426	120	26.23		
				45640	77.8	79.3	1.5	2.70	2766	131	29.87		
				45641	79.3	80.8	1.5	2.70	2402	112	25.31		
				45642	80.8	82.3	1.5	2.70	2153	115	24.77		

DEPTH (meters) FROM TO		Recov ery (%)	Description	Sample No.	From (m)	To (m)	Length (m)	P (g/cm ³)	Ni (%)	Co (ppm)	Mg (%)	Cr (%)	NiS ppm
				45643	82.3	83.8	1.5	2.70	2243	111	23.82		
				45644	83.8	85.3	1.5	2.67	2345	114	25.12		
				45645	85.3	86.8	1.5	2.67	2227	117	23.94		
				45646	86.8	88.3	1.5	2.67	2404	117	24.71		
				45647	88.3	89.8	1.5	2.67	2157	98	23.35		
				45648	89.8	91.3	1.5	2.67	2250	108	23.70		
				45649	91.3	92.8	1.5	2.64	2213	110	24.45		
				45650	92.8	94.3	1.5	2.64	2351	111	25.26		
				45651	94.3	95.8	1.5	2.64	2236	114	26.21		
				45652	95.8	97.3	1.5	2.65	2287	114	25.25		
				45653	97.3	98.8	1.5	2.64	2251	115	24.14		
				45654	98.8	100.3	1.5	2.64	2179	111	23.79		
				45655	100.3	101.8	1.5	2.58	2034	98	22.45		
				45656	101.8	103.3	1.5	2.58	2408	113	24.09		
				45657	103.3	104.8	1.5	2.58	2207	106	24.58		
				45658	104.8	106.3	1.5	2.58	2425	114	25.09		
				45659	106.3	107.8	1.5	2.70	2123	109	24.22		
				45660	107.8	109.3	1.5	2.70	2394	115	25.84		
				45661	109.3	110.8	1.5	2.70	2196	112'	24.19		
				45662	110.8	112.3	1.5	2.70	2135	96	19.59		
				45663	112.3	113.8	1.5	2.70	2325	110	24.70		
				45664	113.8	115.3	1.5	2.70	2424	112	25.34		
				45665	115.3	116.8	1.5	2.66	2378	105	25.40		
				45666	116.8	118.3	1.5	2.66	1992	71	20.22	8.67	949
				45667	118.3	119.8	1.5	2.66	2250	190	22.40	6.14	1068
				45668	119.8	121.3	1.5	2.66	2334	150	24.41	2.96	998
				45669	121.3	122.8	1.5	2.66	2547	113	26.34		
				45670	122.8	124.6	1.8	2.66	2633	120	27.53		

END OF HOLE

DIAMOND DRILL HOLE RECORD

PROPERTY: RECORD RIDGE SOUTH

DDH RRS08-31

DIP AND AZIMUTH TESTS			CORE SIZE: NQ	TOTAL DEPTH: 154.5 m	DATE STARTED: August 28, 2008
DEPTH	ANGLE	AZIMUTH	HOLE ANGLE: - 90°	HOLE AZIMUTH °	DATE FINISHED: Sept. 5, 2008
154.5m	-89.3°	301.4°	SECTION:	COLLAR ELEVATION: 1518.7m	ANALYSIS BY: Assayers Canada
			GRID LOCATION: 175S/ 1425W	RECOVERY:	LOGGED BY: H.K. & C.P.
			UTM (NAD 83): 5432714N 434477E	CLAIM: Frank Sr. 3	CORE STORED AT: Midnight camp

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni %	Co ppm	Mg %
0	3.6		CASING								
3.6	31.9	95	MONZOSYENITE Grey matrix with feldspar phenocrysts up to 12mm, mafic phenocrysts (hbl, px) up to 3-5mm and biotite flakes up to 1-2mm, highly fragmented to pulverized in places, upper 14m looks like a regolithic rock that has been weathered to a sandy/ soil state, lower contact is 60° to c.a. and lined with talcy-calcareous material. 23.8-24.0m is a muddy fault zone.	45816	3.6	5.6	2.0	2.8	164	24	4.39
				45817	5.6	7.6	2.0	2.8	66	24	2.04
				45818	7.6	9.6	2.0	2.8	42	23	1.87
				45819	9.6	11.6	2.0	2.8	37	24	1.83
				45820	11.6	13.6	2.0	2.8	50	23	2.16
				45821	13.6	15.6	2.0	2.8	46	21	2.58
				45822	15.6	17.6	2.0	2.8	48	22	2.44
				45823	17.6	19.6	2.0	2.8	44	22	1.98
				45824	19.6	21.6	2.0	2.8	35	24	1.99
				45825	21.6	23.6	2.0	2.8	32	22	1.76
				45826	23.6	25.6	2.0	2.8	35	24	1.93
				45827	25.6	27.6	2.0	2.8	32	21	1.71
				45828	27.6	29.6	2.0	2.8	32	22	2.02
				45829	29.6	31.9	2.3	2.8	111	26	2.89
31.9	154.5	100	SERPENTINITE Homogeneously black, magnetic, contains webs of magnetite throughout, also contains "silver-looking" sericite flakes (1-2%) 131.0 – 132.2 : yellowish green soapstone 3 – 7 cm, parallel to core axis; occupying 40% of core End of Hole	45830	31.9	33.5	1.5	2.64	2196	123	28.29
				45831	33.5	35.0	1.5	2.64	2091	119	28.21
				45832	35.0	36.5	1.5	2.64	2198	124	29.41
				45833	36.5	38.0	1.5	2.64	2244	128	29.80
				45834	38.0	39.5	1.5	2.64	2035	119	26.73
				45835	39.5	41.0	1.5	2.64	2107	122	29.50
				45836	41.0	42.5	1.5	2.64	2202	127	28.94
				45837	42.5	44.0	1.5	2.64	2043	115	27.77
				45838	44.0	45.5	1.5	2.64	2003	113	27.27
				45839	45.5	47.0	1.5	2.64	1659	99	24.17
				45840	47.0	48.5	1.5	2.64	1947	109	26.87
				45841	48.5	50.0	1.5	2.64	1979	108	27.57
				45842	50.0	51.5	1.5	2.64	1995	109	27.97

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni %	Co ppm	Mg %
				45843	51.5	53.0	1.5	2.64	2067	117	27.17
				45844	53.0	54.5	1.5	2.64	1915	125	27.77
				45845	54.5	56.0	1.5	2.64	2035	119	28.27
				45846	56.0	57.5	1.5	2.64	2107	121	27.87
				45847	57.5	59.0	1.5	2.64	1755	105	25.67
				45848	59.0	60.5	1.5	2.64	2051	119	25.97
				45849	60.5	62.0	1.5	2.64	1923	114	26.77
				45850	62.0	63.5	1.5	2.64	1931	109	25.57
				45851	63.5	65.0	1.5	2.64	2035	114	28.07
				45852	65.0	66.5	1.5	2.64	2003	115	27.27
				45853	66.5	68.0	1.5	2.64	1987	110	27.77
				45854	68.0	69.5	1.5	2.64	1875	107	27.47
				45855	69.5	71.0	1.5	2.64	1939	112	26.77
				45856	71.0	72.5	1.5	2.64	2035	114	27.87
				45857	72.5	74.0	1.5	2.64	2091	114	29.27
				45858	74.0	75.5	1.5	2.64	2139	119	28.27
				45859	75.5	77.0	1.5	2.64	1769	115	28.47
				45860	77.0	78.5	1.5	2.64	1863	115	29.05
				45861	78.5	80.0	1.5	2.64	1934	116	28.80
				45862	80.0	81.5	1.5	2.64	1832	113	27.86
				45863	81.5	83.0	1.5	2.64	1852	123	29.45
				45864	83.0	84.5	1.5	2.64	1854	118	28.89
				45865	84.5	86.0	1.5	2.64	1954	118	29.9
				45866	86.0	87.5	1.5	2.64	2058	123	29.32
				45867	87.5	89.0	1.5	2.64	1987	131	29.55
				45868	89.0	90.5	1.5	2.64	1661	103	29.72
				45869	90.5	92.0	1.5	2.67	1838	124	28.20
				45870	92.0	93.5	1.5	2.67	2012	121	29.15
				45871	93.5	95.0	1.5	2.67	1951	122	28.44
				45872	95.0	96.5	1.5	2.64	2040	120	29.26
				45873	96.5	98.0	1.5	2.64	1912	116	28.72
				45874	98.0	99.5	1.5	2.64	1909	112	28.02
				45875	99.5	101.0	1.5	2.64	1776	118	27.07
				45876	101.0	102.5	1.5	2.64	1708	128	27.64
				45877	102.5	104.0	1.5	2.64	1798	116	27.75
				45878	104.0	105.5	1.5	2.64	1857	120	27.59
				45879	105.5	107.0	1.5	2.64	1850	117	26.93
				45880	107.0	108.5	1.5	2.64	1995	131	28.08
				45881	108.5	110.0	1.5	2.64	2152	125	27.88
				45882	110.0	111.5	1.5	2.64	2041	120	27.58
				45883	111.5	113.0	1.5	2.64	2033	120	28.44
				45884	113.0	114.5	1.5	2.64	2075	117	28.35
				45885	114.5	116.0	1.5	2.64	2096	119	29.01

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni %	Co ppm	Mg %
				45886	116.0	117.5	1.5	2.64	2050	116	26.83
				45887	117.5	119.0	1.5	2.64	1981	110	27.73
				45888	119.0	120.5	1.5	2.64	2091	120	28.61
				45889	120.5	122.0	1.5	2.64	2014	115	27.74
				45890	122.0	123.5	1.5	2.64	2125	126	28.28
				45891	123.5	125.0	1.5	2.64	2116	117	28.09
				45892	125.0	126.5	1.5	2.64	1997	114	27.44
				45893	126.5	128.0	1.5	2.64	1957	112	27.37
				45894	128.0	129.5	1.5	2.64	1993	116	27.60
				45895	129.5	131.0	1.5	2.62	1996	113	27.36
				45896	131.0	132.2	1.2	2.53	1706	103	28.60
				45897	132.2	133.7	1.5	2.70	2098	122	29.05
				45898	133.7	135.2	1.5	2.64	2025	113	28.19
				45899	135.2	136.7	1.5	2.64	2000	116	27.63
				45900	136.7	138.2	1.5	2.64	1923	110	27.52
				45901	138.2	139.7	1.5	2.64	2117	110	24.23
				45902	139.7	141.2	1.5	2.64	1987	106	24.34
				45903	141.2	142.7	1.5	2.64	2145	116	24.76
				45904	142.7	144.2	1.5	2.64	2039	109	25.29
				45905	144.2	145.7	1.5	2.68	2204	118	25.71
				45906	145.7	147.2	1.5	2.65	2278	121	27.37
				45907	147.2	148.7	1.5	2.65	2201	118	25.81
				45908	148.7	150.2	1.5	2.65	2186	114	25.83
				45909	150.2	151.7	1.5	2.64	2120	112	26.23
				45910	151.7	153.2	1.5	2.64	2132	113	25.74
				45911	153.2	154.5	1.3	2.64	2162	118	25.83

END OF HOLE

DIAMOND DRILL HOLE RECORD

PROPERTY: RECORD RIDGE SOUTH

DDH RRS08-32

DIP AND AZIMUTH TESTS			CORE SIZE: NQ	TOTAL DEPTH: 114.8 m	DATE STARTED: August 20, 2008
DEPTH	ANGLE	AZIMUTH	HOLE ANGLE: - 90°	HOLE AZIMUTH °	DATE FINISHED: August 24, 2008
	°	000°	SECTION:	COLLAR ELEVATION: 1504.5m	ANALYSIS BY: Assayers Canada
			GRID LOCATION: 149S/ 1365W	RECOVERY:	LOGGED BY: H.K. & C.P.
			UTM (NAD 83): 5432740N 434537E	CLAIM: Frank Sr. 3	CORE STORED AT: Midnight camp

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni %	Co ppm	Mg %
0	0.0		CASING								
0.0	2.0	100	Rusted weathered rock Lower contact with serpentinite is sharp and 30° to c.a.	45435	0.0	2.0	2.0	2.68	2186	113	22.37
2.0	36.5	100	SERPENTINITE Black to dark-grey, mainly consists of calc-talcy blebs and thinly banded magnetite veinlets/streaks running through the c.a. at 45° to c.a.	45436	2.0	3.5	1.5	2.7	2365	116	25.18
				45437	3.5	5.0	1.5	2.7	2440	118	25.62
				45438	5.0	6.5	1.5	2.7	2332	112	24.76
				45439	6.5	8.0	1.5	2.68	2314	109	24.84
				45440	8.0	9.5	1.5	2.68	2270	110	24.60
				45441	9.5	11.0	1.5	2.68	2320	114	24.34
				45442	11.0	12.5	1.5	2.68	2198	111	24.23
				45443	12.5	14.0	1.5	2.68	2141	102	24.65
				45444	14.0	15.5	1.5	2.68	2233	107	24.53
				45445	15.5	17.0	1.5	2.68	2195	106	22.95
				45446	17.0	18.5	1.5	2.68	2176	103	24.45
				45447	18.5	20.0	1.5	2.68	2250	107	23.28
				45448	20.0	21.5	1.5	2.68	2247	109	24.14
				45449	21.5	23.0	1.5	2.68	2551	121	26.59
				45450	23.0	24.5	1.5	2.7	2353	114	24.49
				45451	24.5	26.0	1.5	2.7	2286	114	25.10
				45452	26.0	27.5	1.5	2.7	2185	105	23.82
				45453	27.5	29.0	1.5	2.7	2092	111	22.37
				45454	29.0	30.5	1.5	2.68	2490	111	24.64
				45455	30.5	32.0	1.5	2.68	1427	89	21.07
				45456	32.0	33.5	1.5	2.68	1189	77	19.06
				45457	33.5	35.0	1.5	2.68	2381	108	23.88
				45458	35.0	36.5	1.5	2.68	2184	89	23.71

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni %	Co ppm	Mg %
36.5	53.3	100	SERPENTINIZED ANDESITE Dark green to green, weakly to non-magnetic, compact, aphanitic, moderately fragmented, hard and strong, but can be readily scratched. Fractures totally coated by soft green serpentine and steatite.	45459 45460 45461 45462 45463 45464 45465 45466 45467 45468 45469	36.5 38.0 39.5 41.0 42.5 44.0 45.5 47.0 48.5 50.0 51.5	38.0 39.5 41.0 42.5 44.0 45.5 47.0 48.5 50.0 51.5 53.3	1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.8	2.7 2.7 2.7 2.7 2.7 2.7 2.7 2.7 2.7 2.7 2.7	532 56 29 30 27 26 29 25 26 31 55	52 41 44 46 46 49 47 46 43 45 41	11.71 4.93 4.42 4.41 4.20 4.38 4.42 4.20 3.77 4.27 4.26
53.3	91.3	100	SERPENTINITE Overall homogeneously black, solid and intact without listwanization; Lower contact is Sharp 45° to c.a. totally filled by green steatite	45470 45471 45472 45473 45474 45475 45476 45477 45478 45479 45480 45481 45482 45483 45484 45485 45486 45487 45488 45489 45490 45491 45492 45493 45494	53.3 54.8 56.3 57.8 59.3 60.8 62.3 63.8 65.3 66.8 68.3 69.8 71.3 72.8 74.3 75.8 77.3 78.8 80.3 81.8 83.3 84.8 86.3 87.8 89.3	54.8 56.3 57.8 59.3 60.8 62.3 63.8 65.3 66.8 68.3 69.8 71.3 72.8 74.3 75.8 77.3 78.8 80.3 81.8 83.3 84.8 86.3 87.8 89.3	1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5	2.68 2.68 2.68 2.65 2.65 2.65 2.65 2.65 2.60 2.60 2.60 2.60 2.74 2.74 2.74 2.61 2.61 2.61 2.68 2.68 2.68 2.58 2.58 2.58	1858 2078 2139 3028 2164 2102 2260 2170 2109 1298 2115 2085 2367 2199 2221 1819 2192 2088 2134 2399 2205 2548 2273 2289 2368	77 88 86 94 96 92 97 98 93 84 106 103 116 109 108 84 103 98 97 113 109 117 103 111 110	19.14 21.03 21.78 21.54 22.17 21.99 21.88 22.98 22.07 16.84 21.36 21.93 24.21 23.85 23.74 21.13 21.98 23.32 22.31 24.28 24.58 25.44 23.19 25.60 23.90
91.3	93.2	100	DIORTIE TO DIAGABBRO Fine to medium grained ; subhedral feldspar phenos and biotite and hornblende in a fine to medium grained groundmass; non-magnetic	45495	91.3	93.2	1.9	2.70	269	52	6.57
93.2	114.8	99	SERPENTINITE In general homogeneously black with green tinge; on megascopic inspection moderately serpentinized with fragmented green	45496 45497 45498 45499	93.2 94.7 96.2 97.7	94.7 96.2 97.7 99.2	1.5 1.5 1.5 1.5	2.69 2.60 2.52 2.45	1877 2289 2244 2222	105 115 114 109	23.50 24.51 24.19 23.33

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni %	Co ppm	Mg %
			serpentine(steatite) at 93.1 – 95.4 and 99.5 – 99.4; upper contact with diorite shows positive intrusive contact features; brecciated serpentinite clasts in diorite.	45500	99.2	100.7	1.5	2.45	1582	84	20.13
				45501	100.7	102.2	1.5	2.60	1877	97	22.05
				45502	102.2	103.7	1.5	2.60	1208	82	19.75
				45503	103.7	105.2	1.5	2.60	2164	105	23.44
				45504	105.2	106.7	1.5	2.60	2436	115	25.33
				45505	106.7	208.2	1.5	2.60	2481	119	26.02
				45506	208.2	109.7	1.5	2.60	2300	111	25.01
				45507	109.7	111.2	1.5	2.60	2493	116	26.17
				45508	111.2	112.7	1.5	2.60	2237	111	24.96
				45509	112.7	114.8	2.1	2.60	2247	107	24.55

END OF HOLE

DIAMOND DRILL HOLE RECORD

PROPERTY: RECORD RIDGE SOUTH

DDH RRS08-33

DIP AND AZIMUTH TESTS			CORE SIZE: NQ	TOTAL DEPTH: 117.3m	DATE STARTED: September 21, 2008
DEPTH	ANGLE	AZIMUTH	HOLE ANGLE: - 90°	HOLE AZIMUTH °	DATE FINISHED: September 24, 2008
	°	000°	SECTION:	COLLAR ELEVATION: 1531.4m	ANALYSIS BY: Assayers Canada
			GRID LOCATION: 153S/ 1475W	RECOVERY:	LOGGED BY: H.K. & C.P.
			UTM (NAD 83): 5432736N 434427E	CLAIM: Frank Sr. 3	CORE STORED AT: Midnight camp

Note: Only selectively assayed for Au, Pt. and Pd - check samples

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm³)	Ni %	Co ppm	Mg %	Pd g/t	Pt g/t	Au g/t
0.0	2.8	50	SHEARED/ FAULTED ZONE Serpentinized andesite moderately rusted & fragmented to pulverized, weakly to non-magnetic.	46353	0.0	2.8	2.8	N/A	1920	102	24.0			
2.8	117.3	100	SERPENTINITE Homogeneously black with magnetite webs, without conspicuous listwanization. 57.2-58.7m is a calcite vein 5cm thick and 20° to the c.a. 95.3-95.6m: Highly fractured with soapstone fractures. 101.7-101.8m: Highly fractured with soapstone fractures. 104.5-105.0m: Highly fractured with soapstone fractures. 116.7-117.3m: Gypsum vein, 10-20cm; cores are highly fragmented to pulverized.	46354	2.8	4.0	1.5	2.69	2086	123	26.88	0.01	0.01	0.01
				46355	4.0	5.5	1.5	2.69	2058	92	22.46			
				46356	5.5	7.0	1.5	2.69	2225	104	26.38			
				46357	7.0	8.5	1.5	2.69	2175	99	25.43			
				46358	8.5	10.0	1.5	2.69	2189	109	25.89			
				46359	10.0	11.5	1.5	2.69	1996	106	25.63			
				46360	11.5	13.0	1.5	2.69	2339	108	28.22			
				46361	13.0	14.5	1.5	2.69	2388	106	28.46			
				46362	14.5	16.0	1.5	2.69	2298	106	26.71			
				46363	16.0	17.5	1.5	2.69	2222	100	26.65			
				46364	17.5	19.0	1.5	2.69	2183	99	24.06			
				46365	19.0	20.5	1.5	2.69	2105	97	25.39			
				46366	20.5	22.0	1.5	2.60	2621	116	28.02			
				46367	22.0	23.5	1.5	2.60	2839	110	25.57			
				46368	23.5	25.0	1.5	2.60	2353	108	27.88			
				46369	25.0	26.5	1.5	2.60	2491	118	28.96			
				46370	26.5	28.0	1.5	2.60	2280	108	25.82	0.01	0.01	0.01
				46371	28.0	29.5	1.5	2.60	2444	120	27.67			
				46372	29.5	31.0	1.5	2.60	2400	111	25.72			
				46373	31.0	32.5	1.5	2.60	2129	102	26.46			
				46374	32.5	34.0	1.5	2.60	2392	108	26.80			
				46375	34.0	35.5	1.5	2.62	2370	107	25.83			
				46376	35.5	37.0	1.5	2.62	2203	102	26.08			
				46377	37.0	38.5	1.5	2.62	2193	101	26.30			
				46378	38.5	40.0	1.5	2.62	2265	109	25.83			
				46379	40.0	41.5	1.5	2.62	1934	101	24.43			
				46380	41.5	43.0	1.5	2.62	2064	100	24.28			

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni %	Co ppm	Mg %	Pd g/t	Pt g/t	Au g/t
				46381	43.0	44.5	1.5	2.62	2059	112	22.03			
				46382	44.5	46.0	1.5	2.62	2353	115	26.51	0.01	0.01	<0.01
				46383	46.0	47.5	1.5	2.62	2440	122	27.37	0.01	0.01	<0.01
				46384	47.5	49.0	1.5	2.62	2343	131	25.38	<0.01	0.01	0.01
				46385	49.0	50.5	1.5	2.60	2167	115	25.37			
				46386	50.5	52.0	1.5	2.60	2243	119	26.07			
				46387	52.0	53.5	1.5	2.60	2123	129	25.32			
				46388	53.5	55.0	1.5	2.60	1520	106	24.25			
				46389	55.0	56.5	1.5	2.60	2289	122	25.03			
				46390	56.5	58.0	1.5	2.60	1952	114	24.38			
				46391	58.0	59.5	1.5	2.60	2077	112	25.22			
				46392	59.5	61.0	1.5	2.68	2226	116	25.64			
				46393	61.0	62.5	1.5	2.68	2362	123	26.74	0.01	0.01	
				46394	62.5	64.0	1.5	2.68	2383	115	27.76	0.01	0.01	
				46395	64.0	65.5	1.5	2.68	2143	104	25.18			
				46396	65.5	67.0	1.5	2.68	2175	118	26.06			
				46397	67.0	68.5	1.5	2.70	2145	121	26.92			
				46398	68.5	70.0	1.5	2.70	2194	115	26.24			
				46399	70.0	71.5	1.5	2.70	2262	126	26.29			
				46400	71.5	73.0	1.5	2.70	2204	120	25.92			
				46401	73.0	74.5	1.5	2.70	2144	109	27.09			
				46402	74.5	76.0	1.5	2.70	2224	117	26.63			
				46403	76.0	77.5	1.5	2.70	2294	113	26.35			
				46404	77.5	79.0	1.5	2.70	2167	112	25.72			
				46405	79.0	80.5	1.5	2.68	2079	113	26.85			
				46406	80.5	82.0	1.5	2.68	2051	105	25.99			
				46407	82.0	83.5	1.5	2.68	2049	103	25.54			
				46408	83.5	85.0	1.5	2.68	2185	109	25.94			
				46409	85.0	86.5	1.5	2.68	2163	107	25.85			
				46410	86.5	88.0	1.5	2.68	2051	103	25.52			
				46411	88.0	89.5	1.5	2.68	2213	108	26.45			
				46412	89.5	91.0	1.5	2.68	2246	110	26.37			
				46413	91.0	92.5	1.5	2.68	2087	110	26.24			
				46414	92.5	94.0	1.5	2.68	1991	108	24.69			
				46415	94.0	95.5	1.5	2.68	1813	94	21.70			
				46416	95.5	97.0	1.5	2.68	2090	109	25.33			
				46417	97.0	98.5	1.5	2.68	2111	107	25.37			
				46418	98.5	100.0	1.5	2.68	2194	110	25.45			
				46419	100.0	101.5	1.5	2.68	2050	112	25.03			
				46420	101.5	103.0	1.5	2.68	2018	105	23.97			
				46421	103.0	104.5	1.5	2.68	1947	105	25.20			
				46422	104.5	106.0	1.5	2.68	1877	103	24.54			
				46423	106.0	107.5	1.5	2.68	2065	104	24.20			

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni %	Co ppm	Mg %	Pd g/t	Pt g/t	Au g/t
				46424	107.5	109.0	1.5	2.68	2098	109	23.37			
				46425	109.0	110.5	1.5	2.68	2111	109	22.92			
				46426	110.5	112.0	1.5	2.68	1885	98	23.12			
				46427	112.0	113.5	1.5	2.68	2241	107	26.14			
				46428	113.5	115.0	1.5	2.68	1750	109	25.15			
				46429	115.0	117.3	2.3	2.68	1957	113	24.78			

END OF HOLE

DIAMOND DRILL HOLE RECORD

PROPERTY: RECORD RIDGE SOUTH

DDH RRS08-34

DIP AND AZIMUTH TESTS			CORE SIZE: NQ	TOTAL DEPTH: 143.0m	DATE STARTED: September 29, 2008
DEPTH	ANGLE	AZIMUTH	HOLE ANGLE: - 90°	HOLE AZIMUTH °	DATE FINISHED: September 30, 2008
143.0m	87.6°	290.3°	SECTION:	COLLAR ELEVATION: 1547.0m	ANALYSIS BY: Assayers Canada
			GRID LOCATION: 188S/ 1541W	RECOVERY:	LOGGED BY: H.K. & C.P.
			UTM (NAD 83): 543701N 434361E	CLAIM: Frank Sr. 3	CORE STORED AT: Midnight camp

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm³)	Ni %	Co ppm	Mg %
0	6.7		CASING								
0.0	5.7	40	SURFACE BOULDERS Monzosyenite & serpentinite								
5.7	7.0	100	SERPENTINITE Sheared & rusted								
7.0	7.7	50	FAULT GOUGE								
7.7	34.0	55	SERPENTINITE Homogeneously black, with magnetite webs, no visible listwanization	46430	7.7	9.2	1.5	2.53	2192	111	25.60
				46431	9.2	10.7	1.5	2.64	2059	109	26.23
				46432	10.7	12.2	1.5	2.64	2042	107	25.47
				46433	12.2	13.7	1.5	2.64	2058	109	26.35
				46434	13.7	15.2	1.5	2.64	2073	113	27.03
				46435	15.2	16.7	1.5	2.64	2192	115	28.82
				46436	16.7	18.2	1.5	2.83	2256	111	29.10
				46437	18.2	19.7	1.5	2.83	2213	117	29.68
				46438	19.7	21.2	1.5	2.83	2207	119	28.88
				46439	21.2	22.7	1.5	2.76	2332	114	30.03
				46440	22.7	24.2	1.5	2.76	2296	112	29.24
				46441	24.2	25.7	1.5	2.76	2252	118	29.20
				46442	25.7	27.2	1.5	2.76	2243	108	29.83
				46443	27.2	28.7	1.5	2.68	2270	112	28.73
				46444	28.7	30.2	1.5	2.68	2070	109	28.75
				46445	30.2	31.7	1.5	2.68	2086	105	26.07
				46446	31.7	32.8	1.1	2.68	1985	104	25.64
				46447	32.8	34.0	1.2	2.7	1984	111	22.58

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni %	Co ppm	Mg %
34.0	39.3	100	SHEARED ZONE Serpentinite	46448	34.0	36.7	2.7	2.70	1248	78	19.81
				46449	36.7	39.3	2.6	2.70	1528	102	20.73
39.3	51.5	100	SERPENTINITE Homogeneously black, with magnetite webs, no visible listwanization	46450	39.3	40.8	1.5	2.7	1991	113	23.94
				46451	40.8	42.3	1.5	2.7	1799	100	23.84
				46452	42.3	43.8	1.5	2.7	2047	116	23.08
				46453	43.8	45.3	1.5	2.7	1815	109	24.31
				46454	45.3	46.8	1.5	2.8	1790	104	24.76
				46455	46.8	48.3	1.5	2.8	1974	111	25.71
				46456	48.3	49.8	1.5	2.8	1837	103	25.03
				46457	49.8	51.5	1.7	2.8	1763	97	23.45
51.5	53.2	85	SHEARED SERPENTINITE Intensely fragmented and chloritized	46458	51.5	53.2	1.7	2.72	1612	97	19.68
53.2	80.2	100	SERPENTINITE Homogeneously black, with magnetite webs, no visible listwanization. 59.2-59.3m is a talcy-cacareous vein, 45° to c.a. 60.7-60.8m is a talc vein, 45° to c.a.	46459	53.2	54.7	1.5	2.68	1807	97	23.36
				46460	54.7	56.2	1.5	2.68	1912	109	24.06
				46461	56.2	57.7	1.5	2.68	1937	107	25.18
				46462	57.7	59.2	1.5	2.68	1929	107	24.44
				46463	59.2	60.7	1.5	2.5	2022	110	24.16
				46464	60.7	62.2	1.5	2.65	2112	113	24.48
				46465	62.2	63.7	1.5	2.65	2004	110	25.15
				46466	63.7	65.2	1.5	2.65	1841	105	23.72
				46467	65.2	67.1	1.5	2.65	1723	96	23.10
				46468	67.1	69.2	1.5	2.65	1943	105	24.01
				46469	69.2	70.7	1.5	2.65	2032	109	25.17
				46470	70.7	72.2	1.5	2.65	1985	114	25.38
				46471	72.2	73.7	1.5	2.67	1869	116	24.44
				46472	73.7	75.2	1.5	2.67	1958	117	24.48
				46473	75.2	76.7	1.5	2.67	1879	110	23.51
				46474	76.7	78.2	1.5	2.67	2041	116	25.19
				46475	78.2	80.2	2.0	2.65	1836	106	22.65
80.2	81.0	100	BASALTIC ANDESITE/ DIAGABBRO Aphanitic to fine-grained, light greenish-grey, non-magnetic, compact, hard, upper contact is filled with gypsum (7cm & 50° to c.a.), lower contact is also filled with gypsum (10cm & 30° to c.a.)	46476	80.2	81.0	0.8	2.57	90	54	5.77
81.0	121.2	100	SERPENTINITE Homogeneously black, with magnetite webs, no visible listwanization. 93.8-94.3m fragmented and chloritized with soapstone fractures. 98.0-98.7m fragmented and chloritized with soapstone fractures. 104.1-104.2m Fault gouge 104.2-104.6m Fragmented and	46477	81.0	82.5	1.5	2.67	1728	108	21.74
				46478	82.5	84.0	1.5	2.67	1988	115	23.69
				46479	84.0	85.5	1.5	2.67	1936	107	24.15
				46480	85.5	87.0	1.5	2.67	1893	124	24.41
				46481	87.0	88.5	1.5	2.67	1919	116	23.70
				46482	88.5	90.0	1.5	2.67	1907	111	23.69
				46483	90.0	91.5	1.5	2.67	2000	114	24.06
				46484	91.5	93.0	1.5	2.67	1860	104	23.18

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni %	Co ppm	Mg %
			chloritized with soapstone fractures.	46485	93.0	94.5	1.5	2.67	1739	98	21.66
				46486	94.5	96.0	1.5	2.67	1633	94	19.27
				46487	96.0	97.5	1.5	2.67	1672	93	19.65
				46488	97.5	99.0	1.5	2.67	1451	78	18.06
				46489	99.0	100.5	1.5	2.67	1845	112	23.53
				46490	100.5	102.0	1.5	2.67	1962	118	24.80
				46491	102.0	103.5	1.5	2.67	1898	115	23.94
				46492	103.5	105.0	1.5	2.65	1877	103	22.29
				46493	105.0	106.5	1.5	2.65	2009	100	24.05
				46494	106.5	108.0	1.5	2.65	2076	107	23.42
				46495	108.0	109.5	1.5	2.65	2242	114	24.84
				46496	109.5	111.0	1.5	2.65	2165	105	23.40
				46497	111.0	112.5	1.5	2.67	1979	105	24.30
				46498	112.5	114.0	1.5	2.67	2384	111	25.13
				46499	114.0	115.5	1.5	2.67	2315	113	25.77
				46500	115.5	117.0	1.5	2.67	2182	113	25.71
				46501	117.0	118.5	1.5	2.67	2102	116	25.81
				46502	118.5	120.0	1.5	2.67	2222	118	26.39
				46503	120.0	121.2	1.2	2.67	1881	102	19.09
121.2	121.9	100	SERPENTINITE Dominated by limono-hematized calcite veins over 70% of the core.	46504	121.2	121.9	0.7	2.67	2084	111	21.11
121.9	124.7	100	SERPENTINITE Homogeneously black, with magnetite webs, no visible listwanization	46505	121.9	123.3	1.4	2.67	2068	115	23.45
				46506	123.3	124.7	1.4		1743	107	20.63
124.7	126.6	100	DIAGABBRO Fine to medium-grained, euhedral to sub- euhedral feldspar phenocrysts up to 3mm, black groundmass, non-magnetic. Upper & lower contacts are 45° to c.a.	46507	124.7	126.6	1.9	2.76	361	66	8.90
126.6	143.0	100	SERPENTINITE Homogeneously black, with magnetite webs, no visible listwanization	46508	126.6	128.1	1.5	2.67	2025	113	24.91
				46509	128.1	129.6	1.5	2.67	2125	117	27.09
				46510	129.6	131.1	1.5	2.67	2250	121	27.35
				46511	131.1	132.6	1.5	2.67	2280	125	28.92
				46512	132.6	134.1	1.5	2.67	2236	123	28.17
				46513	134.1	135.6	1.5	2.67	2307	126	28.39
				46514	135.6	137.1	1.5	2.67	2165	122	29.00
				46515	137.1	138.6	1.5	2.67	2292	125	29.07
				46516	138.6	140.1	1.5	2.67	2536	118	30.05
				46517	140.1	141.6	1.5	2.67	2486	127	30.01
				46518	141.6	143.0	1.4	2.67	2304	123	28.69

END OF HOLE

DIAMOND DRILL HOLE RECORD
RECORD RIDGE SOUTH

DDH RRS08-35

DIP AND AZIMUTH TESTS			CORE SIZE: NQ	TOTAL DEPTH: 123.7m	DATE STARTED: Sept. 11, 2008
DEPTH	ANGLE	AZIMTH	HOLE ANGLE: - 90°	HOLE AZIMUTH °	DATE FINISHED: Sept. 13, 2008
123.7m	-89.0°	247.9°	SECTION:	COLLAR ELEVATION: 1543.3m	ANALYSIS BY: Assayers Canada
			GRID LOCATION: 228S/ 1529W	RECOVERY:	LOGGED BY: H.K. & C.P.
			UTM (NAD 83): 5432661N 434373E	CLAIM: Frank Sr. 3	CORE STORED AT: Midnight camp

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni %	Co ppm	Mg %
0	0		CASING								
0	1.0	25	MONZOSYENITE Fragmented								
1.0	38.4	100	SERPENTINITE Dark-grey to black, magnetite webbing with talcy-calcareous blebs up to 20%, strongly magnetic.	46070	1.0	2.5	1.5	3.0	2994	136	31.1
				46071	2.5	4.0	1.5	3.0	2751	132	29.85
				46072	4.0	5.5	1.5	3.0	2972	139	31.18
				46073	5.5	7.0	1.5	3.0	2691	133	30.80
				46074	7.0	8.5	1.5	2.98	2711	128	29.96
				46075	8.5	10.1	1.5	2.98	2639	130	29.84
				46076	10.1	11.5	1.5	2.98	2729	137	29.49
				46077	11.5	13.0	1.5	2.98	2780	139	29.91
				46078	13.0	14.5	1.5	2.98	2620	126	29.53
				46079	14.5	16.0	1.5	2.91	2841	141	30.66
				46080	16.0	17.5	1.5	2.91	2636	120	29.66
				46081	17.5	19.0	1.5	2.91	2524	128	29.54
				46082	19.0	20.5	1.5	2.93	2814	126	29.94
				46083	20.5	22.0	1.5	2.93	3167	140	28.83
				46084	22.0	23.5	1.5	2.93	2710	131	29.63
				46085	23.5	25.0	1.5	2.93	2628	129	29.97
				46086	25.0	26.5	1.5	2.85	2636	120	29.51
				46087	26.5	28.0	1.5	2.85	2790	126	30.11
				46088	28.0	29.5	1.5	2.85	1993	118	28.34
				46089	29.5	31.0	1.5	2.87	2242	115	26.90
				46090	31.0	32.5	1.5	2.87	2380	121	27.43
				46091	32.5	34.0	1.5	2.75	2205	113	25.54
				46092	34.0	35.5	1.5	2.75	2332	121	25.07
				46093	35.5	37.0	1.5	2.75	2100	116	24.41
				46094	37.0	38.4	1.4	2.75	2181	135	26.12

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni %	Co ppm	Mg %
38.4	40.6	100	DIAGABBRO Medium to coarse grained, lower contact is sharp & 30° to c.a., contact is coated with soapstone	46095	38.4	40.6	2.2	2.65	301	63	7.72
40.6	77.1	100	SERPENTINITE Dark-grey to black, magnetite webbing with talcy-calcareous blebs up to 40%, strongly magnetic.	46096	40.6	42.1	1.5	2.65	2272	129	25.87
				46097	42.1	43.6	1.5	2.65	2299	130	26.73
				46098	43.6	45.1	1.5	2.65	2051	106	24.27
				46099	45.1	46.6	1.5	2.65	2125	108	24.33
				46100	46.6	48.1	1.5	2.65	2033	109	25.03
				46101	48.1	49.6	1.5	2.65	1951	104	25.17
				46102	49.6	51.1	1.5	2.69	2248	120	28.25
				46103	51.1	52.6	1.5	2.69	2440	124	29.67
				46104	52.6	54.1	1.5	2.62	2310	125	30.61
				46105	54.1	55.6	1.5	2.62	2278	122	29.50
				46106	55.6	57.1	1.5	2.68	2008	112	28.10
				46107	57.1	58.6	1.5	2.68	1906	116	27.24
				46108	58.6	60.1	1.5	2.65	2058	109	26.63
				46109	60.1	61.6	1.5	2.65	1868	104	24.81
				46110	61.6	63.1	1.5	2.80	1971	112	25.37
				46111	63.1	64.6	1.5	2.80	2318	123	30.14
				46112	64.6	66.1	1.5	2.72	2188	121	26.74
				46113	66.1	67.6	1.5	2.72	2121	116	28.35
				46114	67.6	69.6	1.5	2.63	2252	114	28.10
				46115	69.6	70.6	1.5	2.65	2118	111	27.78
				46116	70.6	72.1	1.5	2.65	2351	123	29.18
				46117	72.1	73.6	1.5	2.65	2174	116	28.12
				46118	73.6	75.1	1.5	2.65	2129	117	25.54
				46119	75.1	77.1	1.5	2.63	2034	114	25.00
77.1	78.0	100	SERPENTINIZED ANDESITE Or dark green serpentinite	46120	77.1	78.0	0.9	2.79	1239	92	24.25
78.0	106.0	100	SERPENTINITE Homogeneously black with magnetite webs, magnetic, "silver-looking" flakes (sericite).	46121	78.0	79.5	1.5	2.66	2479	130	27.79
				46122	79.5	81.0	1.5	2.66	2328	133	29.30
				46123	81.0	82.5	1.5	2.33	2360	126	27.88
				46124	82.5	84.0	1.5	2.53	2069	122	25.74
				46125	84.0	85.5	1.5	2.66	1433	100	23.62
				46126	85.5	87.0	1.5	2.66	2201	112	26.24
				46127	87.0	88.5	1.5	2.62	2207	122	27.72
				46128	88.5	90.0	1.5	2.49	1755	103	24.58
				46129	90.0	91.5	1.5	2.49	2307	117	25.22
				46130	91.5	93.0	1.5	2.59	2206	117	26.65
				46131	93.0	94.5	1.5	2.59	2198	122	28.09
				46132	94.5	96.0	1.5	2.68	2209	115	26.81
				46133	96.0	97.5	1.5	2.68	2260	122	27.58

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni %	Co ppm	Mg %
				46134	97.5	99.0	1.5	2.70	2311	121	27.0
				46135	99.0	100.5	1.5	2.7	2257	115	26.62
				46136	100.5	102.0	1.5	2.58	2239	117	26.65
				46137	102.0	103.5	1.5	2.57	2126	110	26.87
				46138	103.5	104.7	1.2	2.58	2284	120	27.76
				46139	104.7	106.0	1.3	2.70	2048	110	25.14
106.0	107.5	100	ANDESITE TO DIAGABBRO Apanitic to fine grained; light greenish grey; Non-magnetic; upper contact sharp coated by soft soapstone 45° to c.a.; lower contact also sharp serpentinized to soapstone 45° to c.a.	46140	106.0	107.5	1.5	2.77	345	70	8.62
107.5	111.3	100	SERPENTINITE Homogeneously black with magnetite webs without conspicuous listwanization	46141	107.5	108.8	1.3	2.53	2150	119	25.18
				46142	108.8	110.1	1.3	2.55	2143	118	25.63
				46143	110.1	111.3	1.2	2.53	2048	105	23.15
111.3	111.6	100	ANDESITE TO DIAGABBRO Similar to previous section	46144	111.3	113.2	1.9	2.70	841	80	12.56
111.6	112.0	50	SHEARED/FAULTED ZONE In mixed serpentine(soapstone and andesite) Highly broken Included in sample 46144								
112.0	113.2	100	DIAGABBRO TO ANDESITE Fairly similar to previous section Included in sample 46144								
113.2	115.6	100	SERPENTINITE Dark greenish grey; moderately magnetic with calcite veining 20° to c.a rusted at random intervals	46145	113.2	114.4	1.2	2.58	1993	118	24.42
				46146	114.4	115.6	1.2	2.58	1862	114	25.40
115.6	123.7	100	SERPENTINITE Homogeneously black with magnetite webs without conspicuous listwanization	46147	115.6	117.0	1.5	2.59	2061	119	26.76
				46148	117.0	118.5	1.5	2.59	2023	127	27.0
				46149	118.5	120.0	1.5	2.68	2118	124	27.97
				46150	120.0	121.5	1.5	2.68	2201	139	28.76
				46151	121.5	123.7	2.2	2.70	2251	128	29.28

END OF HOLE

DDH RRS08-36

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni %	Co ppm	Mg %
0	1.5		CASING								
0	2.1	65	FRAGMENTED/ RUSTED SERPENTINITE Highly broken and moderately limo-hematized, dark-grey serpentinite with magnetite webbing, strongly magnetic.	45987	0.0	2.1	2.1	2.5	2129	111	22.24
2.1	107.8	100	SERPENTINITE Homogeneously black with magnetite webbing, lacks any listwanization. - Moderately fragmented with soapstone from 17.9-19.3m - Serpentinized andesite from 49.3 to 50.8; black with green tinge	45988	2.1	3.5	1.4	2.5	1998	106	23.58
				45989	3.5	5.0	1.5	2.5	1860	99	23.01
				45990	5.0	6.5	1.5	2.5	1991	101	22.78
				45991	6.5	8.0	1.5	2.5	1954	107	22.60
				45992	8.0	9.5	1.5	2.5	1953	102	23.31
				45993	9.5	11.0	1.5	2.75	2107	111	23.97
				45994	11.0	12.5	1.5	2.75	1781	94	22.67
				45995	12.5	14.0	1.5	2.75	1969	108	23.80
				45996	14.0	15.5	1.5	2.68	2014	113	24.66
				45997	15.5	16.7	1.2	2.68	2093	112	24.21
				45998	16.7	17.9	1.2	2.68	2060	124	23.92
				45999	17.9	19.3	1.5	2.67	446	69	17.76
				46000	19.3	20.8	1.5	2.67	1737	96	21.35
				46001	20.8	22.3	1.5	2.67	2076	101	23.12
				46002	22.3	23.8	1.5	2.67	2154	112	25.84
				46003	23.8	25.3	1.5	2.65	2164	109	24.97
				46004	25.3	26.8	1.5	2.65	2206	111	24.10
				46005	26.8	28.3	1.5	2.65	1968	106	24.18
				46006	28.3	29.8	1.5	2.61	2108	121	25.77
				46007	29.8	31.3	1.5	2.61	2238	119	27.37
				46008	31.3	32.8	1.5	2.64	2291	117	26.29
				46009	32.8	34.3	1.5	2.64	2205	110	26.00

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni %	Co ppm	Mg %
				46010	34.3	35.8	1.5	2.64	2153	109	25.60
				46011	35.8	37.3	1.5	2.63	2200	112	24.08
				46012	37.3	38.8	1.5	2.63	2080	113	24.67
				46013	38.8	40.3	1.5	2.63	2140	119	24.74
				46014	40.3	41.8	1.5	2.61	2194	114	23.39
				46015	41.8	43.3	1.5	2.61	2049	112	26.15
				46016	43.3	44.8	1.5	2.61	2129	114	24.27
				46017	44.8	46.3	1.5	2.61	2184	109	24.71
				46018	46.3	47.8	1.5	2.83	1962	106	23.60
				46019	47.8	49.3	1.5	2.83	1777	109	21.42
				46020	49.3	50.8	1.5	2.83	189	61	9.82
				46021	50.8	52.3	1.5	2.75	1602	93	21.12
				46022	52.3	53.8	1.5	2.75	1319	94	17.76
				46023	53.8	55.3	1.5	2.75	1841	115	25.82
				46024	55.3	56.8	1.5	2.8	1764	116	25.13
				46025	56.8	58.3	1.5	2.8	1917	119	25.55
				46026	58.3	59.8	1.5	2.8	2136	130	26.76
				46027	59.8	61.3	1.5	2.84	1986	123	26.20
				46028	61.3	62.8	1.5	2.84	1818	111	25.62
				46029	62.8	64.3	1.5	2.84	1774	108	25.0
				46030	64.3	65.8	1.5	2.84	1718	109	24.56
				46031	65.8	67.3	1.5	2.62	1835	109	25.07
				46032	67.3	68.8	1.5	2.62	1873	117	24.28
				46033	68.8	70.3	1.5	2.63	1966	121	26.02
				46034	70.3	71.8	1.5	2.63	1909	111	27.43
				46035	71.8	73.3	1.5	2.63	2125	129	27.13
				46036	73.3	74.8	1.5	2.63	1907	118	27.90
				46037	74.8	76.3	1.5	2.63	1878	117	27.57
				46038	76.3	77.8	1.5	2.63	1886	115	27.58
				46039	77.8	79.3	1.5	2.69	1994	122	27.89
				46040	79.3	80.8	1.5	2.69	2242	137	29.75
				46041	80.8	82.3	1.5	2.69	2321	132	30.89
				46042	82.3	83.8	1.5	2.7	2308	140	31.59
				46043	83.8	85.3	1.5	2.7	2116	126	28.73
				46044	85.3	86.8	1.5	2.7	2090	124	27.89
				46045	86.8	88.3	1.5	2.63	2137	110	25.53
				46046	88.3	89.8	1.5	2.65	2050	117	25.63
				46047	89.8	91.3	1.5	2.65	2050	114	26.98
				46048	91.3	92.8	1.5	2.65	2211	116	28.26
				46049	92.8	94.3	1.5	2.65	2246	115	27.23
				46050	94.3	95.8	1.5	2.65	2240	113	28.02
				46051	95.8	97.3	1.5	2.65	2052	105	24.82
				46052	97.3	98.8	1.5	2.65	1834	101	22.07

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni %	Co ppm	Mg %
				46053	98.8	100.3	1.5	2.65	738	73	1629
				46054	100.3	101.8	1.5	2.65	2215	112	24.84
				46055	101.8	103.3	1.5	2.65	856	73	17.65
				46056	103.3	104.8	1.5	2.65	2073	114	23.59
				46057	104.8	106.3	1.5	2.65	1930	104	25.39
				46058	106.3	107.8	1.5	2.65	2209	118	19.18
107.8	110.2	100	SERPENTINIZED ANDESITE Dark green, strong hard	46059	107.8	110.2	2.4	2.65	57	26	6.91
110.2	124.4	100	SERPENTINITE Homogeneously black with magnetite webbing, lacks any listwanization.	46060	110.2	110.8	0.6	2.65	1002	82	17.50
				46061	110.8	112.3	1.5	2.65	2134	111	24.06
				46062	112.3	113.8	1.5	2.65	2240	110	24.98
				46063	113.8	115.3	1.5	2.65	2191	116	26.63
				46064	115.3	116.8	1.5	2.65	2178	120	28.38
				46065	116.8	118.3	1.5	2.65	1991	112	26.09
				46066	118.3	119.8	1.5	2.65	2236	110	25.59
				46067	119.8	121.3	1.5	2.65	2440	116	26.29
				46068	121.3	122.8	1.5	2.65	2530	118	26.85
				46069	122.8	124.4	1.6	2.65	2400	113	26.1

END OF HOLE

DIAMOND DRILL HOLE RECORD

PROPERTY: RECORD RIDGE SOUTH

DDH RRS08-37

DIP AND AZIMUTH TESTS			CORE SIZE: NQ	TOTAL DEPTH: 123.7m	DATE STARTED: Sept. 3th, 2008
DEPTH	ANGLE	AZIMUTH	HOLE ANGLE: - 90°	HOLE AZIMUTH °	DATE FINISHED: Sept. 10th, 2008
123.7m	-87.7°	320.7°	SECTION:	COLLAR ELEVATION: 1525.2m	ANALYSIS BY: Assayers Canada
			GRID LOCATION: 249S/ 1471W	RECOVERY:	LOGGED BY: H.K. & C.P.
			UTM (NAD 83): 5432640N 434431E	CLAIM: Frank Sr. 3	CORE STORED AT: Midnight camp

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm³)	Ni %	Co ppm	Mg %
0	4.3	70	CASING								
4.3	8.3	90	FAULT GOUGE Muddy, pulverized chunks of weathered rock >5cm in length. Appear to have a monzosyenite protolith.					2.13			
8.3	14.9	100	MONZOSYENITE Somewhat fragmented, grey matrix with feldspar phenocrysts up to 10mm, mafic phenocrysts (px, hbl) up to 5mm and biotite flakes 1-2mm, hard, non-magnetic, Lower contact is 40° to c.a. and shows a thick infusion zone (~5-7cm), which is line with talcy-calcareous material.	45912 45913 45914	8.3 10.3 12.3	10.3 12.3 14.9	2.0 2.0 2.6	2.7 2.7 2.7	110 39 256	24 22 34	2.48 2.03 4.59
14.9	17.0	100	SERPENTINITE Hybrid zone between the black serpentinite below and the monzosyenite above, milky white mixed with light-green serpentine, magnetic, intact.	45915	14.9	17.0	2.1	2.65	1728	108	20.66
17.0	70.8	100	SERPENTINITE Homogeneously black, magnetic, intact core, magnetite webbing throughout. "Silver looking" sericite flakes throughout (1-2%) Top contact appears to be a hydrothermal exhalative zone from the monzosyenite above.	45916 45917 45918 45919 45920 45921 45922 45923 45924 45925 45926 45927	17.0 18.5 20.0 21.5 23.0 24.5 26.0 27.5 29.0 30.5 32.0 33.5	18.5 20.0 21.5 23.0 24.5 26.0 27.5 29.0 30.5 32.0 33.5 35.0	1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5	2.68 2.60 2.60 2.60 2.64 2.64 2.64 2.64 2.64 2.64 2.64 2.64	2210 2079 2125 2157 2059 2008 2142 2143 2025 2039 1886 2079	120 115 118 117 110 110 115 115 109 109 106 109	24.31 23.81 24.09 24.86 23.99 23.47 25.34 24.33 24.35 25.29 23.28 23.88

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni %	Co ppm	Mg %
				45928	35.0	36.5	1.5	2.64	1984	109	24.06
				45929	36.5	38.0	1.5	2.64	1958	106	23.86
				45930	38.0	39.5	1.5	2.64	1950	115	24.08
				45931	39.5	41.0	1.5	2.64	2013	109	23.83
				45932	41.0	42.5	1.5	2.64	1972	102	23.29
				45933	42.5	44.0	1.5	2.64	1833	97	23.29
				45934	44.0	45.5	1.5	2.64	2114	110	25.08
				45935	45.5	47.0	1.5	2.66	2082	112	25.40
				45936	47.0	48.5	1.5	2.66	2120	108	25.02
				45937	48.5	50.0	1.5	2.66	2041	106	24.53
				45938	50.0	51.5	1.5	2.66	1972	109	23.42
				45939	51.5	53.0	1.5	2.71	2051	113	24.72
				45940	53.0	54.5	1.5	2.71	2066	114	25.57
				45941	54.5	56.0	1.5	2.71	2047	111	25.22
				45942	56.0	57.5	1.5	2.71	2116	112	25.26
				45943	57.5	59.0	1.5	2.68	1916	123	25.58
				45944	59.0	60.5	1.5	2.68	2106	115	24.84
				45945	60.5	62.0	1.5	2.68	2101	106	23.91
				45946	62.0	63.5	1.5	2.73	2065	112	24.17
				45947	63.5	65.0	1.5	2.73	2056	114	25.47
				45948	65.0	66.5	1.5	2.73	2042	120	24.10
				45949	66.5	68.0	1.5	2.64	2138	112	25.53
				45950	68.0	69.5	1.5	2.64	2108	118	25.36
				45951	69.5	70.8	1.3	2.64	1929	120	25.11
70.8	72.6	100	SERPENTINE Mixed serpentine and milky-white serpentine, fragmented with talcy-calcareous fractures, moderately magnetic.	45952	70.8	72.6	1.8	2.65	1469	96	20.94
72.6		100	SERPENTINITE Homogeneously black, magnetic, intact core, magnetite webbing throughout. “Silver looking” sericite flakes throughout (1-2%) • Network of talcy-calcareous fractures from 86.0-86.7m	45953	72.6	74.1	1.5	2.68	2008	112	24.14
				45954	74.1	75.6	1.5	2.68	2105	110	24.73
				45955	75.6	77.1	1.5	2.68	2173	116	25.83
				45956	77.1	78.6	1.5	2.68	1869	111	24.62
				45957	78.6	80.1	1.5	2.65	2125	116	24.33
				45958	80.1	81.6	1.5	2.65	2135	117	25.12
				45959	81.6	83.1	1.5	2.65	2015	110	24.13
				45960	83.1	84.6	1.5	2.65	2043	109	23.92
				45961	84.6	86.1	1.5	2.65	2139	118	23.85
				45962	86.1	87.6	1.5	2.65	1856	102	22.75
				45963	87.6	89.1	1.5	2.65	2072	113	24.80
				45964	89.1	90.6	1.5	2.65	1219	81	15.83
				45965	90.6	92.1	1.5	2.65	2246	117	25.72
				45966	92.1	93.6	1.5	2.65	2064	109	24.72
				45967	93.6	95.1	1.5	2.65	2070	115	26.61
				45968	95.1	96.6	1.5	2.73	2138	115	25.31

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni %	Co ppm	Mg %
				45969	96.6	98.1	1.5	2.73	2189	115	26.17
				45970	98.1	99.6	1.5	2.73	2108	112	25.84
				45971	99.6	101.1	1.5	2.66	2153	114	25.38
				45972	101.1	102.6	1.5	2.66	2190	116	26.77
				45973	102.6	104.1	1.5	2.66	1816	100	21.99
				45974	104.1	105.6	1.5	2.66	2047	108	23.62
				45975	105.6	107.1	1.5	2.66	1927	106	24.66
				45976	107.1	108.6	1.5	2.66	2251	119	27.09
				45977	108.6	110.1	1.5	2.8	2230	118	26.57
				45978	110.1	111.6	1.5	2.8	2328	122	27.23
				45979	111.6	113.1	1.5	2.82	2251	119	26.74
				45980	113.1	114.6	1.5	2.82	1992	102	23.70
				45981	114.6	116.1	1.5	2.82	2200	113	26.05
				45982	116.1	117.6	1.5	2.82	2145	112	25.81
				45983	117.6	119.1	1.5	2.82	2278	117	26.23
				45984	119.1	120.6	1.5	2.82	2238	123	26.68
				45985	120.6	122.1	1.5	2.83	2313	119	27.44
				45986	122.1	123.7	1.6	2.83	2422	125	27.51

END OF HOLE

DIAMOND DRILL HOLE RECORD

PROPERTY: RECORD RIDGE SOUTH

DDH RRS08-38

DIP AND AZIMUTH TESTS			CORE SIZE: NQ	TOTAL DEPTH: 154.2m	DATE STARTED: August 28, 2008
DEPTH	ANGLE	AZIMUTH	HOLE ANGLE: - 90°	HOLE AZIMUTH °	DATE FINISHED: Sept. 3, 2008
154.2m	-89.7°	073.8°	SECTION:	COLLAR ELEVATION: 1514.7m	ANALYSIS BY: Assayers Canada
			GRID LOCATION: 14+75W / 300 S	RECOVERY:	LOGGED BY: H.K. & C.P.
			UTM (NAD 83): 5432589N 434427E	CLAIM: Frank Sr. 3	CORE STORED AT: Midnight camp

DEPTH (meters) FROM TO		Recover y (%)	Description	Sample No.	From (m)	To (m)	Length (m)	P (g/cm ³)	Ni (%)	Co (ppm)	Mg (%)
			Casing to 6.7 m								
0	7.0	16	SHEARED/FAULTED ZONE in Monzosyenite; rusted ,weathered and highly broken cores; lower contact is healed by green serpentine	45717	0	7.0	7.0	2.56	602	46	7.19
7.0	7.2	100	FAULT GOUGE Included in sample 45718								
7.2	8.4	100	SERPENTINITE Dark green to black with green tinge, compact and hard	45718	7.0	8.4	1.4	2.70	2323	133	26.31
8.4	8.45	100	FAULT GOUGE 50° to c.a.								
8.45	11.6	100	SERPENTINITE Dark green, compact and hard but can be scratched easily	45719 45720	8.4 10.0	10.0 11.6	1.6 1.6	2.57 2.57	2010 2053	113 114	24.98 22.63
11.6	41.95	100	SERPENTINITE Homogeneously black with sporadic magnetite webbing at random intervals; overall solid intact cores, silver looking flakes (2-5%)	45721 45722 45723 45724 45725 45726 45727 45728 45729 45730 45731 45732	11.6 13.0 14.5 16.0 17.5 19.0 20.5 20.5 22.0 23.5 25.0 26.5 28.0	13.0 14.5 16.0 17.5 19.0 20.5 22.0 23.5 25.0 26.5 28.0 29.5	1.4 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5	2.67 2.67 2.67 2.62 2.62 2.62 2.68 2.68 2.68 2.58 2.58 2.60	1368 1981 2125 2016 2121 2023 1854 2001 2045 2070 2033 2097	95 118 117 117 116 110 115 118 113 121 114 124	19.17 25.89 25.66 26.78 26.01 26.11 26.21 26.20 27.42 27.01 27.76 29.60

DEPTH (meters) FROM TO		Recover y (%)	Description	Sample No.	From (m)	To (m)	Length (m)	P (g/cm ³)	Ni (%)	Co (ppm)	Mg (%)
				45733	29.5	31.0	1.5	2.60	2295	132	27.65
				45734	31.0	32.5	1.5	2.60	2259	129	27.07
				45735	32.5	34.0	1.5	2.7	2085	116	26.90
				45736	34.0	35.5	1.5	2.7	1987	101	23.87
				45737	35.5	37.0	1.5	2.7	1366	87	19.12
				45738	37.0	38.5	1.5	2.73	1976	109	26.47
				45739	38.5	40.0	1.5	2.73	1990	122	25.93
				45740	40.0	41.95	1.95	2.73	1087	88	18.89
41.95	42.8	100	DIAGABBRO Medium grained, grey with pyroxene phenocrysts (1-2mm), fragmented, top and bottom contacts are sharp and 60° to c.a.	45741	41.95	42.8	0.85	2.76	83	47	6.13
42.8	105.8	100	SERPENTINITE Homogeneously black with sporadic magnetite webbing at random intervals; overall solid intact cores, silver looking flakes (2-5%)	45742	42.8	44.3	1.5	2.7	2052	117	27.67
				45743	44.3	45.8	1.5	2.7	1974	117	27.91
				45744	45.8	47.3	1.5	2.7	2173	127	29.07
				45745	47.3	48.8	1.5	2.71	1891	117	29.17
				45746	48.8	50.3	1.5	2.71	2046	126	29.08
				45747	50.3	51.8	1.5	2.71	2027	120	27.58
				45748	51.8	53.3	1.5	2.71	1911	121	27.90
				45749	53.3	54.8	1.5	2.72	1979	127	29.47
				45750	54.8	56.3	1.5	2.72	2258	135	29.47
				45751	56.3	57.8	1.5	2.72	1871	113	23.71
				45752	57.8	59.3	1.5	2.7	1868	119	27.42
				45753	59.3	60.8	1.5	2.7	1808	108	26.69
				45754	60.8	62.3	1.5	2.7	2021	120	28.89
				45755	62.3	63.8	1.5	2.7	1814	116	28.45
				45756	63.8	65.3	1.5	2.7	2175	133	29.15
				45757	65.3	66.8	1.5	2.7	2233	132	30.34
				45758	66.8	68.3	1.5	2.82	2289	135	31.30
				45759	68.3	69.8	1.5	2.82	1918	120	27.46
				45760	69.8	71.3	1.5	2.82	2153	134	30.85
				45761	71.3	72.8	1.5	2.82	2127	124	28.26
				45762	72.8	74.3	1.5	2.82	2057	122	27.70
				45763	74.3	75.8	1.5	2.82	1932	119	27.44
				45764	75.8	77.3	1.5	2.82	2046	133	27.94
				45765	77.3	78.8	1.5	2.82	2262	141	28.90
				45766	78.8	80.3	1.5	2.82	2419	148	29.78
				45767	80.3	81.8	1.5	2.82	2389	143	30.71
				45768	81.8	83.3	1.5	2.86	2382	142	29.48
				45769	83.3	84.8	1.5	2.86	2220	127	29.73
				45770	84.8	86.3	1.5	2.86	2159	125	28.89
				45771	86.3	87.8	1.5	2.86	1806	116	28.10

DEPTH (meters) FROM TO		Recover y (%)	Description	Sample No.	From (m)	To (m)	Length (m)	P (g/cm ³)	Ni (%)	Co (ppm)	Mg (%)
				45772	87.8	89.3	1.5	2.86	1839	112	26.21
				45773	89.3	90.8	1.5	2.86	2098	127	28.14
				45774	90.8	92.3	1.5	2.86	2183	126	28.44
				45775	92.3	93.8	1.5	2.86	2096	125	28.29
				45776	93.8	95.3	1.5	2.8	2126	139	28.88
				45777	95.3	96.8	1.5	2.8	2118	124	28.87
				45778	96.8	98.3	1.5	2.8	2168	124	29.36
				45779	98.3	99.8	1.5	2.8	1951	122	27.51
				45780	99.8	101.3	1.5	2.78	2213	139	27.79
				45781	101.3	102.8	1.5	2.78	2215	127	27.78
				45782	102.8	104.3	1.5	2.78	2120	122	28.29
				45783	104.3	105.8	1.5	2.78	1797	85	20.69
105.8	122.3	100	SERPENTINITE Black with milky-white sections & talc-calcareous fractures throughout, strongly magnetic, somewhat fragmented by the network of fractures, still contains “silver-looking” sericite flakes	45784	105.8	107.3	1.5	2.8	2173	116	25.34
				45785	107.3	108.8	1.5	2.8	1651	79	18.88
				45786	108.8	110.3	1.5	2.8	1618	79	19.87
				45787	110.3	111.8	1.5	2.8	1665	79	18.95
				45788	111.8	113.3	1.5	2.8	1822	88	19.54
				45789	113.3	114.8	1.5	2.8	1828	89	18.74
				45790	114.8	116.3	1.5	2.8	2260	117	25.34
				45791	116.3	117.8	1.5	2.8	1712	84	19.25
				45792	117.8	119.3	1.5	2.8	1686	85	19.02
				45793	119.3	120.8	1.5	2.82	1773	85	19.41
				45794	120.8	122.25	1.45	2.82	1692	85	19.57
122.25	154.2	100	SERPENTINITE Homogeneously black with sporadic magnetite webbing at random intervals; overall solid intact cores, silver looking flakes (2-5%)	45795	122.25	123.8	1.5	2.81	1769	91	20.43
				45796	123.8	125.3	1.5	2.81	1949	97	19.78
				45797	125.3	126.8	1.5	2.81	1933	96	21.07
				45798	126.8	128.3	1.5	2.82	1948	96	20.42
				45799	128.3	129.8	1.5	2.82	1929	95	20.36
				45800	129.8	131.3	1.5	2.82	1788	91	20.84
				45801	131.3	132.8	1.5	2.82	2277	130	31.16
				45802	132.8	134.3	1.5	2.82	2422	133	33.84
				45803	134.3	135.8	1.5	2.82	2088	130	29.97
				45804	135.8	137.3	1.5	2.82	2350	129	31.32
				45805	137.3	138.8	1.5	2.82	2473	134	33.30
				45806	138.8	140.3	1.5	2.81	2165	125	29.79
				45807	140.3	141.8	1.5	2.81	2335	132	32.77
				45808	141.8	143.3	1.5	2.81	2362	141	30.94
				45809	143.3	144.8	1.5	2.81	2332	131	31.34
				45810	144.8	146.3	1.5	2.8	2263	126	29.80
				45811	146.3	147.8	1.5	2.8	2400	137	30.63
				45812	147.8	149.3	1.5	2.8	2324	127	30.68
				45813	149.3	150.8	1.5	2.8	2360	131	31.17
				45814	150.8	152.3	1.5	2.8	2463	125	31.96
				45815	152.3	154.2	1.9	2.8	2392	135	32.45

END OF HOLE

DIAMOND DRILL HOLE RECORD

PROPERTY: RECORD RIDGE SOUTH

DDH RRS08-39

DIP AND AZIMUTH TESTS			CORE SIZE: NQ	TOTAL DEPTH: 154.5m	DATE STARTED: September 19, 2008
DEPTH	ANGLE	AZIMUTH	HOLE ANGLE: - 90°	HOLE AZIMUTH °	DATE FINISHED: September 22, 2008
154.5m	-88.2°	248.1°	SECTION:	COLLAR ELEVATION: 1530.9m	ANALYSIS BY: Assayers Canada
			GRID LOCATION: 275S/ 1525W	RECOVERY:	LOGGED BY: H.K. & C.P.
			UTM (NAD 83): 5432614N 434377E	CLAIM: Frank Sr. 3	CORE STORED AT: Midnight camp

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni %	Co ppm	Mg %
0	0.9		CASING to 0.9 m Surface boulders of monzosyenite								
0.9	5.4	100	SERPENTINITE Black with some listwanization; talc-calcose blebs and magnetite web; upper 1 m section is hemato-limonitized	46250 46251 46252	0.9 2.4 3.9	2.4 3.9 5.4	1.5 1.5 1.5	2.73 2.73 2.73	2246 2080 2115	129 120 121	28.42 27.60 27.78
5.4	26.5	100	SERPENTINITE Homogeneously black with magnetite webs throughout the section	46253 46254 46255 46256 46257 46258 46259 46260 46261 46262 46263 46264 46265 46266	5.4 7.0 8.5 10.0 11.5 13.0 14.5 16.0 17.5 19.0 20.5 22.0 23.5 25.0 25.0	7.0 8.5 10.0 11.5 13.0 14.5 16.0 17.5 19.0 20.5 22.0 23.5 25.0 26.5	1.6 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5	2.78 2.78 3.81 2.81 2.83 2.83 2.74 2.74 2.76 2.76 2.69 2.69 2.70 2.70	2021 2020 2088 2027 2121 2012 1975 2010 1940 2080 1919 2064 2060 2031	119 121 121 117 124 115 109 113 111 112 109 110 113 118	28.44 28.76 28.15 27.91 28.43 28.09 27.11 26.58 27.49 27.37 27.12 27.68 27.85 27.67
26.5	26.6	100	FAULT GOUGE Included in sample 46267 below								
26.6	28.0	100	SERPENTINITE Homogeneously black with magnetite webs throughout the section	46267	26.5	28.0	1.5	2.70	2054	115	26.90
28.5	32.5	100	SERPENTINITE Dominated by yellow green steatite veins and veinlets parallel to c.a. consisting over 50 % of core	46268 46269 46270	28.0 29.5 31.0	29.5 31.0 32.5	1.5 1.5 1.5	2.67 2.67 2.58	2020 2138 2336	116 110 149	25.91 25.43 29.18

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni %	Co ppm	Mg %
32.5	103.5	100	SERPENTINITE Homogeneously black with magnetite webs throughout the section	46271	32.5	34.0	1.5	2.71	2154	117	27.73
				46272	34.0	35.5	1.5	2.59	2161	118	28.0
				46273	35.5	37.0	1.5	2.55	2137	111	27.34
				46274	37.0	38.5	1.5	2.55	2163	112	27.51
				46275	38.5	40.0	1.5	2.59	2112	110	25.90
				46276	40.0	41.5	1.5	2.59	2120	107	24.50
				46277	41.5	43.0	1.5	2.58	2946	114	26.57
				46278	43.0	44.5	1.5	2.58	2114	112	27.11
				46279	44.5	46.0	1.5	2.67	2032	104	26.56
				46280	46.0	47.5	1.5	2.67	2085	108	26.71
				46281	47.5	49.0	1.5	2.63	2120	117	27.75
				46282	49.0	50.5	1.5	2.63	2114	114	27.40
				46283	50.5	52.0	1.5	2.83	1839	104	25.37
				46284	52.0	53.5	1.5	2.83	2110	114	26.91
				46285	53.5	55.0	1.5	2.61	2116	117	26.73
				46286	55.0	56.5	1.5	2.61	2022	113	26.18
				46287	56.5	58.0	1.5	2.73	2040	112	27.52
				46288	58.0	59.5	1.5	2.73	2019	110	26.92
				46289	59.5	61.0	1.5	2.70	2064	120	28.40
				46290	61.0	62.5	1.5	2.70	2080	119	28.60
				46291	62.5	64.0	1.5	2.67	2008	116	28.51
				46292	64.0	65.5	1.5	2.67	2080	117	27.70
				46293	65.5	67.0	1.5	2.55	2064	116	28.20
				46294	67.0	68.5	1.5	2.55	2088	119	29.20
				46295	68.5	70.0	1.5	2.56	1944	115	27.70
				46296	70.0	71.5	1.5	2.56	2168	129	31.10
				46297	71.5	73.0	1.5	2.65	2024	113	28.70
				46298	73.0	74.5	1.5	2.65	1432	100	21.30
				46299	74.5	76.0	1.5	2.57	1888	110	26.80
				46300	76.0	77.5	1.5	2.63	2032	122	27.80
				46301	77.5	79.0	1.5	2.63	1912	109	28.20
				46302	79.0	80.5	1.5	2.68	1992	117	29.50
				46303	80.5	82.0	1.5	2.68	1944	112	28.50
				46304	82.0	83.5	1.5	2.68	2032	116	29.20
				46305	83.5	85.0	1.5	2.60	2080	118	27.40
				46306	85.0	86.5	1.5	2.60	2056	117	28.40
				46307	86.5	88.0	1.5	2.60	1592	109	23.50
				46308	88.0	89.5	1.5	2.68	1856	108	26.40
				46309	89.5	91.0	1.5	2.68	1936	114	27.00
				46310	91.0	92.5	1.5	2.72	2048	118	28.20
				46311	92.5	94.0	1.5	2.72	2171	116	23.30
				46312	94.0	95.5	1.5	2.71	2010	110	23.47
				46313	95.5	97.0	1.5	2.71	2004	111	23.30

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni %	Co ppm	Mg %
				46314 46315 46316 46317	97.0 98.5 100.0 101.5	98.5 100.0 101.5 103.5	1.5 1.5 1.5 2.0	2.71 2.68 2.68 2.68	1836 1996 2020 2053	111 112 115 116	22.32 23.96 21.59 22.16
103.5	104.3	100	SERPENTINIZED ANDESITE Contains soapstone, highly fragmented and pulverized, non-magnetic.	46318	103.5	105.3	1.8	2.72	1260	90	16.15
104.3	105.3	100	SERPENTINITE Milky-white, rusted								
105.3	113.8	100	SERPENTINITE Homogeneously black with magnetite webs throughout the section	46319 46320 46321 46322 46323 46324	105.3 106.8 108.3 109.8 111.3 112.8	106.8 108.3 109.8 111.3 112.8 113.8	1.5 1.5 1.5 1.5 1.5 1.0	2.63 2.63 2.63 2.63 2.63 2.63	1997 1981 2041 1965 1922 1932	116 110 112 115 108 109	23.08 22.50 23.14 23.02 22.56 22.55
113.8	114.8	100	SERPENTINITE Milky-white, moderately sheared (Fragmented) and pulverized into talcy soapstone, upper contact is 50° to c.a.	46325	113.8	114.8	1.0	2.54	1895	106	21.05
114.8	136.4	100	SERPENTINITE Homogeneously black with magnetite webs throughout the section. Highly pulverized soapstone from 125.0-125.3m	46326 46327 46328 46329 46330 46331 46332 46333 46334 46335 46336 46337 46338 46339	114.8 116.3 117.8 119.3 120.8 122.3 123.8 125.3 126.8 128.3 129.8 131.3 132.8 134.3	116.3 117.8 119.3 120.8 122.3 123.8 125.3 126.8 128.3 129.8 131.3 132.8 134.3 136.4	1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 2.1	2.73 2.73 2.73 2.73 2.73 2.73 2.73 2.73 2.73 2.73 2.73 2.63 2.63	1906 1978 1973 1845 1846 1878 1902 1905 2017 2288 2034 2206 2148 2238	109 109 115 110 109 107 110 109 114 130 115 123 128 131	21.71 23.00 22.99 22.66 23.21 22.08 22.00 26.61 27.61 29.52 26.42 29.57 30.16 30.56
136.4	137.0	100	ANDESITE/ DIAGABBRO Upper contact is 60° to c.a., lower contact is 70° to c.a.	46340	136.4	137.0	0.6	2.65	313	77	12.33
137.0	154.5	100	SERPENTINITE Homogeneously black with magnetite webs throughout the section	46341 46342 46343 46344 46345 46346	137.0 138.5 140.0 141.5 143.5 144.5	138.5 140.0 141.5 143.5 144.5 146.0	1.5 1.5 1.5 1.5 1.5 1.5	2.63 2.63 2.63 2.63 2.63 2.63	2046 2247 2205 2014 2247 2235	120 130 126 121 128 131	27.18 28.65 28.27 28.84 29.26 29.90

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni %	Co ppm	Mg %
				46347	146.0	147.5	1.5	2.63	2336	134	31.09
				46348	147.5	149.0	1.5	2.63	2193	133	30.44
				46349	149.0	150.5	1.5	2.68	2249	134	31.50
				46350	150.5	152.0	1.5	2.68	2263	133	31.62
				46351	152.0	153.5	1.5	2.68	2115	124	27.95
				46352	153.5	154.5	1.0	2.68	2290	132	28.64

END OF HOLE

DIAMOND DRILL HOLE RECORD

PROPERTY: RECORD RIDGE SOUTH

DDH RRS08-40

DIP AND AZIMUTH TESTS			CORE SIZE: NQ	TOTAL DEPTH: 148.4 m	DATE STARTED: September 12, 2008
DEPTH	ANGLE	AZIMUTH	HOLE ANGLE: - 90°	HOLE AZIMUTH °	DATE FINISHED: September 17, 2008
148.4	-89.4°	289.2°	SECTION:	COLLAR ELEVATION: 1517.3m	ANALYSIS BY: Assayers Canada
			GRID LOCATION: 325S/ 1528W	RECOVERY:	LOGGED BY: H.K. & C.P.
			UTM (NAD 83): 5432564N 434374E	CLAIM: Frank Sr. 3	CORE STORED AT: Midnight camp

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm³)	Ni %	Co ppm	Mg %
			CASING to 1.5 m								
0	0.2		Boulders of monzosyenite								
0.2	11.8	100	SERPENTINITE Homogeneously black with rich magnetite webs without conspicuous listwanization Except calcite vein at 21.8 - 22.8	46152 46153 46154 46155 46156 46157 46158	0.2 2.1 3.6 5.1 6.6 8.1 9.6	2.1 3.6 5.1 6.6 8.1 9.6 11.8	1.9 1.5 1.5 1.5 1.5 1.5 2.2	2.65 2.68 2.68 2.68 2.76 2.76 2.81	2125 2322 2178 2058 2165 2116 2068	131 149 134 133 134 140 125	28.07 28.11 28.73 29.10 28.63 28.72 27.18
11.8	12.3	100	QUARTZ-CALCITE VEIN & SERPENTINITE in serpentinite; about 50 % of core is Q-C vein material parallel to c.a.	46159	11.8	12.3	0.5		1200	87	23.71
12.3	23.1	100	SERPENTINITE Homogeneously black with rich magnetite webs without conspicuous listwanization	46160 46161 46162 46163 46164 46165 46166	12.3 13.8 15.3 16.8 18.3 19.8 21.3	13.8 15.3 16.8 18.3 19.8 21.3 23.1	1.5 1.5 1.5 1.5 1.5 1.5 1.8	2.87 2.87 2.74 2.74 2.86 2.86 2.86	2240 2195 2055 1135 2091 2117 2045	127 127 132 99 126 124 122	28.19 28.10 26.06 20.77 27.33 28.50 27.30
23.1	26.6	100	ANDESITE TO DIAGABBRO Light greenish, aphanitic to fine-grained; non-magnetic; megascopically porphyroblastic; upper contact sharp 20° to c.a. ; lower contact also sharp 45° to c.a coated by green soapstone	46167 46168	23.1 24.8	24.8 26.6	1.7 1.8	2.84 2.84	52 77	35 42	3.71 4.28

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni %	Co ppm	Mg %
26.6	71.1	100	SERPENTINITE Homogeneously black with rich magnetite webs without conspicuous listwanization Except: sections of 52.3 – 53.6 and 55.6 – 57.5 are dominated by soapstone and weak to moderately magnetic	46169	26.6	28.1	1.5	2.67	1983	109	28.01
				46170	28.1	29.6	1.5	2.67	1926	107	28.19
				46171	29.6	31.1	1.5	2.56	1854	104	28.33
				46172	31.1	32.6	1.5	2.47	1866	105	27.68
				46173	32.6	34.1	1.5	2.70	2061	107	28.10
				46174	34.1	35.6	1.5	2.70	2031	105	27.90
				46175	35.6	37.1	1.5	2.68	2099	105	29.27
				46176	37.1	38.6	1.5	2.66	2004	111	29.68
				46177	38.6	40.1	1.5	2.66	2207	109	28.86
				46178	40.1	41.6	1.5	2.60	2010	109	28.72
				46179	41.6	43.1	1.5	2.60	1868	101	27.21
				46180	43.1	44.6	1.5	2.60	1968	108	28.40
				46181	44.6	46.1	1.5	2.58	1929	106	28.16
				46182	46.1	47.6	1.5	2.58	1942	102	27.84
				46183	47.6	49.1	1.5	2.74	1973	104	27.47
				46184	49.1	50.6	1.5	2.74	1864	102	27.71
				46185	50.6	52.2	1.6	2.55	2007	105	26.72
				46186	52.2	53.6	1.4	2.48	1730	97	23.88
				46187	53.6	55.6	2.0	2.48	1981	105	26.62
				46188	55.6	57.5	1.9	2.68	1855	101	26.38
				46189	57.5	59.0	1.5	2.47	2046	111	25.69
				46190	59.0	60.5	1.5	2.68	2069	111	25.73
				46191	60.5	62.0	1.5	2.68	2170	113	26.27
				46192	62.0	63.5	1.5	2.68	2018	111	25.84
				46193	63.5	65.0	1.5	2.68	2101	110	27.74
				46194	65.0	66.5	1.5	2.66	2047	118	25.50
				46195	66.5	68.0	1.5	2.66	2148	117	26.54
				46196	68.0	69.5	1.5	2.79	2129	110	25.77
				46197	69.5	71.1	1.6	2.79	2286	117	27.72
71.1	76.4	100	SERPENTINITE Mixed with soft soapstone at random intervals 75.1 – 71.7 : dominated by soapstone 75.1 – 75.3 : same as above 75.6 – 76.8 : same as above 76.1 – 76.4 : same as above	46198	71.1	72.8	1.7	2.52	2004	106	26.11
				46199	72.8	74.3	1.7	2.52	2208	114	26.14
				46200	74.3	76.4	2.1	2.50	2073	106	25.12
76.4	85.5	100	SERPENTINITE Homogeneously black without listwanization, solid intact except soapstone at 79.0 – 79.3	46201	76.4	77.9	1.5	2.74	2073	112	23.41
				46202	77.9	79.4	1.5	2.74	2127	110	24.38
				46203	79.4	80.9	1.5	2.59	2177	119	25.03
				46204	80.9	82.4	1.5	2.59	2150	108	23.70
				46205	82.4	83.9	1.5	2.68	2120	107	24.10
				46206	83.9	85.5	1.6	2.47	2252	112	25.23
85.5	86.7	100	ANDESITE Light greenish grey; aphanitic and non-magnetic; upper contact sharp 50° to c.a;	46207	85.5	86.7	1.2	2.70	159	63	6.06

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni %	Co ppm	Mg %
			lower contact also sharp 30° to c.a								
86.7	89.7	100	SERPENTINITE Dark grey to black; moderately listwanized with calc-talcoose webs and srtringers	46208 46209	86.7 88.2	88.2 89.7	1.5 1.5	2.87 2.74	2168 1914	113 111	24.50 23.35
89.7	126.7	100	SERPENTINITE Homogeneously black with rich magnetite webs without conspicuous listwanization	46210 46211 46212 46213 46214 46215 46216 46217 46218 46219 46220 46221 46222 46223 46224 46225 46226 46227 46228 46229 46230 46231 46232 46233 46234	89.7 91.2 92.7 94.2 95.7 97.2 98.7 100.2 101.7 103.2 104.7 106.2 107.7 109.2 110.7 112.2 113.7 115.2 116.7 118.2 119.7 121.2 122.7 124.2 125.7	91.2 92.7 94.2 95.7 97.2 98.7 100.2 101.7 103.2 104.7 106.2 107.7 109.2 110.7 112.2 113.7 115.2 116.7 118.2 119.7 121.2 122.7 124.2 127.0	1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.3	2.53 2.53 2.43 2.48 2.54 2.63 2.63 2.73 2.73 2.50 2.54 2.58 2.56 2.65 2.65 2.64 2.64 2.57 2.57 2.67 2.67 2.72 2.72 2.75 2.66	2012 2098 2216 2006 2159 2132 2211 1987 2142 2085 2141 2128 2197 2293 2255 2220 2329 2118 2208 2208 2219 2260 2231 2226 1314	104 105 108 103 115 106 112 100 109 110 113 113 119 100 105 111 107 102 106 98 101 107 98 101 88	23.60 23.71 24.64 23.80 25.67 25.45 25.00 23.10 24.84 24.64 25.59 25.43 25.12 23.30 24.53 24.45 24.83 22.31 21.93 23.57 24.13 22.60 23.71 22.34 15.87
126.7	127.0	100	ANDESITE Light green, ahanitic; non-magnetic Included in sample # 46235				0.3				
127.0	140.3	100	SERPENTINITE Homogeneously black with rich magnetite webs without conspicuous listwanization	46235 46236 46237 46238 46239 46240 46241 46242 46243	127.0 128.5 130.0 131.5 133.0 134.5 136.0 137.5 139.0	128.5 130.0 131.5 133.0 134.5 136.0 137.5 139.0 140.3	1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.3	2.59 2.68 2.71 2.64 2.65 2.72 2.71 2.60 2.80	2151 2107 2080 2052 2559 2512 2410 2264 2374	101 99 111 98 119 124 121 107 114	22.55 22.44 23.45 24.50 27.07 27.17 26.81 28.64 25.81

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni %	Co ppm	Mg %
140.3	141.8	100	SERPENTINITE Mixed with soapstone fractures about 20%	46244	140.3	141.8	1.5	2.80	2134	103	23.99
141.8	144.0	100	SERPENTINITE Homogeneously black with rich magnetite webs without conspicuous listwanization	46245 46246	141.8 142.9	142.9 144.0	1.1 1.1	2.88 2.88	2031 2184	118 121	26.82 28.67
144.0	145.9	100	SERPENTINITE Dominated by soft green talcy soapstone parallel to c.a.	46247	144.0	145.9	1.9	2.73	1781	102	26.39
145.9	148.4	100	SERPENTINITE Homogeneously black with rich magnetite webs without conspicuous listwanization	46248 46249	145.9 147.4	147.4 148.4	1.5 1.0	2.80 2.80	2295 2422	132 131	30.48 30.75

END OF HOLE

DIAMOND DRILL HOLE RECORD

PROPERTY RECORD RIDGE SOUTH

DDH RRS08-41

DIP AND AZIMUTH TESTS			CORE SIZE: NQ	TOTAL DEPTH: 88.1m	DATE STARTED: October 1, 2008
DEPTH	ANGLE	AZIMUTH	HOLE ANGLE: - 90°	HOLE AZIMUTH °	DATE FINISHED: October 2, 2008
88.1m	-89.4°	203.6°	SECTION:	COLLAR ELEVATION: 1492.8m	ANALYSIS BY: Assayers Canada
			GRID LOCATION: 175S/ 1325W	RECOVERY:	LOGGED BY: H.K. & C.P.
			UTM (NAD 83): 5432714N 434577E	CLAIM: Frank Sr. 3	CORE STORED AT: Midnight camp

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm³)	Ni %	Co ppm	Mg %
0	1.5	40	CASING								
1.5	19.9	100	SERPENTINITE Homogeneously black, magnetite webs.	46519	0.0	2.0	2.0	2.54	2148	113	26.68
				46520	2.0	3.5	1.5	2.54	2011	110	26.88
				46521	3.5	5.0	1.5	2.54	2212	116	26.30
				46522	5.0	6.5	1.5	2.54	2172	119	26.50
				46523	6.5	8.0	1.5	2.68	2095	112	27.68
				46524	8.0	9.5	1.5	2.68	1973	106	25.95
				46525	9.5	11.0	1.5	2.68	2059	112	27.27
				46526	11.0	12.5	1.5	2.63	2069	112	27.67
				46527	12.5	14.0	1.5	2.63	2056	116	27.58
				46528	14.0	15.5	1.5	2.63	2063	115	27.01
				46529	15.5	17.0	1.5	2.63	2069	115	26.32
				46530	17.0	18.5	1.5	2.64	2033	113	25.51
				46531	18.5	19.9	1.4	2.64	2137	115	25.54
19.9	20.7	100	FAULT ZONE Consists of gouge and pulverized serpentinite, upper contact is 50° to c.a.	46532	19.9	20.7	0.8	2.68	103	29	6.63
20.7	49.3	100	MONZOSYENITE Coarse grained, euhedral phenocrysts up to 4mm os biotite and hornblende, milky-pink groundmass, both contacts are in fault zones and pulverized.	46533	20.7	22.0	2.0	2.68	82	27	2.89
				46534	22.0	24.0	2.0	2.68	41	27	2.22
				46535	24.0	26.0	2.0	2.68	37	22	1.93
				46536	26.0	28.0	2.0	2.68	37	25	2.18
				46537	28.0	30.0	2.0	2.68	40	27	2.12
				46538	30.0	32.0	2.0	2.68	48	28	2.23
				46539	32.0	34.0	2.0	2.68	33	25	2.01
				46540	34.0	36.0	2.0	2.68	35	26	2.01
				46541	36.0	38.0	2.0	2.68	36	25	2.01
				46542	38.0	40.0	2.0	2.68	33	26	1.97
				46543	40.0	42.0	2.0	2.68	34	25	1.97
				46544	42.0	44.0	2.0	2.68	35	26	2.08

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni %	Co ppm	Mg %
				46545	44.0	46.0	2.0	2.68	35	26	2.16
				46546	46.0	48.0	2.0	2.68	90	26	2.97
				46547	48.0	49.3	1.3	2.68	37	21	2.51
49.3	83.7	100	SERPENTINITE Homogeneously black, magnetite webs. 56.3-56.5 Sheared with soapstone fractures. 59.4-60.7m Sheared with soapstone fractures.	46548	49.3	50.8	1.5	2.54	1722	94	21.48
				46549	50.8	52.3	1.5	2.54	1773	111	21.32
				46550	52.3	53.8	1.5	2.62	1623	93	18.16
				46551	53.8	55.3	1.5	2.62	2220	117	25.43
				46552	55.3	56.8	1.5	2.62	2228	114	26.76
				46553	56.8	58.3	1.5	2.62	1859	111	26.29
				46554	58.3	59.8	1.5	2.62	2022	112	25.66
				46555	59.8	61.3	1.5	2.62	2080	107	25.32
				46556	61.3	62.8	1.5	2.62	2102	112	25.93
				46557	62.8	64.3	1.5	2.62	2078	116	26.00
				46558	64.3	65.8	1.5	2.62	2287	123	27.07
				46559	65.8	67.3	1.5	2.62	2242	119	27.46
				46560	67.3	68.8	1.5	2.62	2136	113	27.92
				46561	68.8	70.3	1.5	2.62	2174	115	27.08
				46562	70.3	71.8	1.5	2.62	2037	105	27.00
				46563	71.8	73.3	1.5	2.62	2127	111	27.43
				46564	73.3	74.8	1.5	2.62	2152	114	25.87
				46565	74.8	76.3	1.5	2.62	2290	112	26.71
				46566	76.3	77.8	1.5	2.62	2326	115	28.06
				46567	77.8	79.3	1.5	2.62	2422	108	27.43
				46568	79.3	80.8	1.5	2.62	2428	118	27.89
				46569	80.8	82.3	1.5	2.62	2338	114	28.25
				46570	82.3	83.7	1.4	2.62	2373	112	26.93
83.7	88.1	100	BASALTIC ANDESITE/ DIAGABBRO Upper contact is 20° to c.a.	46571	83.7	85.2	1.5	2.72	794	65	13.87
				46572	85.2	86.7	1.5	2.72	185	52	6.58
				46573	86.7	88.1	1.4	2.72	159	59	8.03

END OF HOLE

DIAMOND DRILL HOLE RECORD

PROPERTY: RECORD RIDGE SOUTH

DDH RRS08-42

DIP AND AZIMUTH TESTS			CORE SIZE: NQ	TOTAL DEPTH: 93.5m	DATE STARTED: October 2, 2008
DEPTH	ANGLE	AZIMUTH	HOLE ANGLE: - 90°	HOLE AZIMUTH °	DATE FINISHED: October 3, 2008
93.5m	-89.8°	222.9°	SECTION:	COLLAR ELEVATION: 1482.5m	ANALYSIS BY: Assayers Canada
			GRID LOCATION: 200S/ 1275W	RECOVERY:	LOGGED BY: H.K. & C.P.
			UTM (NAD 83): 5432689N 434627E	CLAIM: Frank Sr. 3	CORE STORED AT: Midnight camp

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm³)	Ni %	Co ppm	Mg %
0	2.1		CASING								
0.0	5.8	70	SHEARED/ FAULTED SERPENTINITE Moderately fragmented and rusted, includes some fault gouge.	46574 46575 46576	0.2 2.6 4.2	2.6 4.2 5.8	2.4 1.6 1.6	2.54 2.54 2.54	1143 2262 2282	72 117 116	13.65 23.51 25.02
5.8	8.2	100	SERPENTINITE Homogeneously black, sporadic calcite veinlets 10-20° to c.a.	46577 46578	5.8 7.0	7.0 8.2	1.2 1.2	2.58 2.68	1917 2128	113 116	25.57 25.31
8.2	9.7	80	SHEARED/ FAULTED BASALTIC ANDESITE Highly fragmented and rusted, lower contact is sharp and 50° to c.a.	46579	8.2	9.7	1.5	n/a	389	73	9.97
9.7	89.5	100	SERPENTINITE Homogeneously black with magnetite webs.	46580 46581 46582 46583 46584 46585 46586 46587 46588 46589 46590 46591 46592 46593 46594 46595 46596 46597 46598	9.7 11.0 12.5 14.0 15.5 17.0 18.5 20.0 21.5 23.0 24.5 26.0 27.5 29.0 30.5 32.0 33.5 35.0 36.5	11.0 12.5 14.0 15.5 17.0 18.5 20.0 21.5 23.0 24.5 26.0 27.5 29.0 30.5 32.0 33.5 35.0 38.0	1.3 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5	2.6 2.6 2.6 2.6 2.6 2.6 2.6 2.6 2.6 2.6 2.6 2.6 2.83 2.83 2.83 2.83 2.83 2.83 2.83	2089 2119 2148 2056 2081 2018 2074 2077 2130 2139 2144 2101 2478 2071 2181 2030 2131 2014 2202	117 116 123 118 119 115 114 117 130 151 116 117 128 108 123 1209 122 117 123	25.92 26.75 26.65 26.08 26.49 25.48 25.96 25.59 26.22 22.49 23.67 24.65 25.99 25.76 25.59 24.83 25.01 24.66 24.91

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni %	Co ppm	Mg %
				46599	38.0	39.5	1.5	2.83	2160	121	24.76
				46600	39.5	41.0	1.5	2.83	2062	115	25.32
				46601	41.0	42.5	1.5	2.83	1971	116	26.04
				46602	42.5	44.0	1.5	2.83	2379	121	25.42
				46603	44.0	45.5	1.5	2.83	2101	129	24.30
				46604	45.5	47.0	1.5	2.83	2128	109	25.42
				46605	47.0	48.5	1.5	2.83	2201	120	25.03
				46606	48.5	50.0	1.5	2.83	2230	118	25.09
				46607	50.0	51.5	1.5	2.63	2145	115	26.07
				46608	51.5	53.0	1.5	2.63	2159	115	24.98
				46609	53.0	54.5	1.5	2.63	2222	120	24.36
				46610	54.5	56.0	1.5	2.63	2074	113	24.07
				46611	56.0	57.5	1.5	2.63	2122	117	23.29
				46612	57.5	59.0	1.5	2.63	2037	114	23.79
				46613	59.0	60.5	1.5	2.63	2230	117	23.30
				46614	60.5	62.0	1.5	2.63	2126	115	24.65
				46615	62.0	63.5	1.5	2.63	2036	113	24.28
				46616	63.5	65.0	1.5	2.63	2012	111	24.56
				46617	65.0	66.5	1.5	2.63	2162	112	24.50
				46618	66.5	68.0	1.5	2.63	2229	111	24.82
				46619	68.0	69.5	1.5	2.63	1899	104	24.83
				46620	69.5	71.0	1.5	2.63	2114	112	24.67
				46621	71.0	72.5	1.5	2.63	2212	117	24.91
				46622	72.5	74.0	1.5	2.63	2103	115	24.50
				46623	74.0	75.5	1.5	2.63	1120	83	16.52
				46624	75.5	77.0	1.5	2.63	1064	87	15.30
				46625	77.0	78.5	1.5	2.63	1925	105	25.68
				46626	78.5	80.0	1.5	2.63	1980	108	25.37
				46627	80.0	81.5	1.5	2.63	1977	106	26.30
				46628	81.5	83.0	1.5	2.63	2060	111	26.31
				46629	83.0	84.5	1.5	2.63	2071	109	26.01
				46630	84.5	86.0	1.5	2.63	2177	119	26.98
				46631	86.0	87.5	1.5	2.63	2099	113	27.33
				46632	87.5	89.5	2.0	2.63	1870	101	21.75
89.5	93.5	100	DIAGABBRO Medium to coarse grained, euhedral to sub- euhedral phenocrysts in the medium to coarse-grained mafic groundmass.	46633 46634	89.5 91.5	91.5 93.5	2.0 2.0	2.7 2.7	571 121	57 31	12.99 4.33

END OF HOLE

DIAMOND DRILL HOLE RECORD

PROPERTY: RECORD RIDGE SOUTH

DDH RRS08-43

DIP AND AZIMUTH TESTS			CORE SIZE: NQ	TOTAL DEPTH: 93.3m	DATE STARTED: October 4, 2008
DEPTH	ANGLE	AZIMUTH	HOLE ANGLE: - 90°	HOLE AZIMUTH °	DATE FINISHED: October 6, 2008
93.3m	-89.6°	243.9°	SECTION:	COLLAR ELEVATION: 1479.4m	ANALYSIS BY: Assayers Canada
			GRID LOCATION: 250S/ 1275W	RECOVERY:	LOGGED BY: H.K. & C.P.
			UTM (NAD 83): 5432639N 434627E	CLAIM: Frank Sr. 3	CORE STORED AT: Midnight camp

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm³)	Ni %	Co ppm	Mg %
0	1.8		CASING								
0.0	1.5	60	SERPENTINITE Highly weathered, “earthy” brown tone, pulverized.								
1.5	6.5	100	SERPENTINITE Black, magnetic, massive, talcy-calcareous filled fractures throughout slightly fragmented.	46635 46636 46637	1.5 3.0 4.5	3.0 4.5 6.5	1.5 1.5 2.0	2.66 2.66 2.66	2140 1980 1722	120 112 93	24.82 23.92 23.51
6.5	36.4	100	SERPENTINITE Homogeneously black, magnetic, magnetite webs throughout. 30.4-30.8m: Talcy-calcareous fractures. 32.1-32.3m: Talcy-calcareous fractures.	46638 46639 46640 46641 46642 46643 46644 46645 46646 46647 46648 46649 46650 46651 46652 46653 46654 46655 46656 46657	6.5 8.0 9.5 11.0 12.5 14.0 15.5 17.0 18.5 20.0 21.5 23.0 24.5 26.0 27.5 27.5 29.0 30.5 30.5 32.0 33.5 33.5 35.0	8.0 9.5 11.0 12.5 14.0 15.5 17.0 18.5 20.0 21.5 23.0 24.5 26.0 27.5 29.0 30.5 32.0 33.5 35.0 36.4	1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.4	2.66 2.66 2.66 2.66 2.62 2.62 2.62 2.57 2.57 2.57 2.66 2.66 2.66 2.66 2.66 2.64 2.64 2.64 2.63 2.63	2022 2188 2121 1920 2039 1991 2019 2097 1954 2172 2002 2002 2079 2009 2140 2220 2095 1714 2019 2105	110 122 111 105 109 109 104 104 106 108 104 103 109 103 114 113 109 101 100 100	24.82 26.52 23.66 24.46 25.26 24.99 26.38 26.88 26.74 26.53 25.96 26.09 26.44 25.69 25.99 25.10 25.38 25.14 25.83 25.07

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni %	Co ppm	Mg %
36.4	38.1	100	SERPENTINIZED ANDESITE Dark grey, fractured throughout, weakly magnetic.	46658	36.4	38.1	1.7	2.67	227	55	15.38
38.1	54.9	100	SERPENTINITE Homogeneously black, magnetic, magnetite webs throughout. 39.8-41.0: Contains some fractures coated with soapstone.	46659 46660 46661 46662 46663 46664 46665 46666 46667 46668 46669	38.1 39.6 41.1 42.6 44.1 45.6 47.1 48.6 50.1 51.6 53.1	39.6 41.1 42.6 44.1 45.6 47.1 48.6 50.1 51.6 53.1 54.9	1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.5 1.8	2.65 2.65 2.57 2.57 2.57 2.61 2.61 2.61 2.56 2.56 2.55	2192 2089 2254 2166 2244 2274 2348 2138 2333 2432 2453	124 103 133 116 104 111 115 107 107 111 110	23.09 25.80 27.13 26.91 26.77 26.58 27.52 26.69 26.78 27.82 27.52
54.9	56.9	100	BASALTIC ANDESITE Dark grey, fragmented, non-magnetic, upper contact is lined with soapstone, sharp and 15° to c.a.	46670	54.9	56.9	2.0	2.80	614	72	11.14
56.9	63.6	100	SERPENTINITE Homogeneously black, magnetic, magnetite webs throughout, upper and lower contacts are sharp and 50° to c.a.	46671 46672 46673 46674 46675	56.9 58.4 59.9 61.4 62.5	58.4 59.9 61.4 62.5 63.6	1.5 1.5 1.5 1.1 1.1	2.55 2.55 2.60 2.60 2.60	2337 2052 2252 2184 2000	103 95 107 108 107	26.74 26.60 27.14 27.40 23.88
63.6	85.0	100	MONZOSYENITE Somewhat fragmented, pinkish, leucocratic groundmass, mafic phenocrysts (hbl & bt) 2-3mm and feldspar phenocrysts 3-4mm. Hard, non-magnetic.	46676 46677 46678 46679 46680 46681 46682 46683 46684 46685 46686	63.6 65.6 67.6 69.6 71.6 73.6 75.6 77.6 79.6 81.6 83.6	65.6 67.6 69.6 71.6 73.6 75.6 77.6 79.6 81.6 83.6 85.0	2.0 2.0 2.0 2.0 2.0 2.0 2.0 2.0 2.0 2.0 1.4	2.65 2.65 2.65 2.65 2.65 2.65 2.65 2.65 2.65 2.65 2.65	168 77 42 54 55 38 44 34 29 28 39	31 26 25 25 55 23 24 24 23 23 25	3.35 2.39 2.13 2.35 8.90 1.92 1.78 1.63 1.75 1.64 1.94
85.0	93.3	100	BASALTIC ANDESITE Dark grey, hard, massive, aphanitic, weakly to non-magnetic, contains calcite stringers at random intervals.	46687 46688 46689 46690	85.0 87.0 89.0 91.0	87.0 89.0 91.0 93.3	2.0 2.0 2.0 2.3	2.70 2.70 2.70 2.70	301 159 46 65	54 45 48 45	6.02 4.82 3.84 3.88

END OF HOLE

DIAMOND DRILL HOLE RECORD

PROPERTY: RECORD RIDGE SOUTH

DDH RRS08-44

DIP AND AZIMUTH TESTS			CORE SIZE: NQ	TOTAL DEPTH: 109.4m	DATE STARTED: October 7, 2008
DEPTH	ANGLE	AZIMUTH	HOLE ANGLE: - 90°	HOLE AZIMUTH °	DATE FINISHED: October 8, 2008
109.4m	-89.7°	358.8°	SECTION:	COLLAR ELEVATION: 1,427.7m	ANALYSIS BY: Assayers Canada
			GRID LOCATION: 600S/1275W	RECOVERY:	LOGGED BY: H.K. & C.P.
			UTM (NAD 83): 5432289N 434627E	CLAIM: Frank Sr. 3	CORE STORED AT: Midnight camp

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm³)	Ni %	Co ppm	Mg %
0	9.8		CASING								
0.0	20.6	25	ANDESITE Dark-grey, weakly to non-magnetic, fractured to pulverized.	46691 46692 46693 46694 46695 46696 46697 46698 46699 46700	0.0 2.0 4.0 6.0 8.0 10.0 12.0 14.0 16.0 18.0	2.0 4.0 6.0 8.0 10.0 12.0 14.0 16.0 18.0 20.6	2.0 2.0 2.0 2.0 2.0 2.0 2.0 2.0 2.0 2.6	n/a n/a n/a n/a n/a 2.76 2.76 2.76 2.76 2.76	38 77 211 336 256 144 118 62 148 141	18 21 28 38 35 34 32 32 31 30	1.50 1.87 3.11 6.67 6.20 3.72 3.85 3.67 2.20 2.74
20.6	22.4	80	FAULT GOUGE plus fragmented andesite	46701	20.6	22.4	1.8	n/a	327	27	2.26
22.4	52.0	100	ANDESITE Hard, grey, compact, somewhat fragmented, non-magnetic.	46702 46703 46704 46705 46706 46707 46708 46709 46710 46711 46712 46713 46714 46715 46716	22.4 24.4 26.4 28.4 30.4 32.4 34.4 36.4 38.4 40.0 42.4 44.4 46.4 48.4 50.4	24.4 26.4 28.4 30.4 32.4 34.4 36.4 38.4 40.0 42.4 44.4 46.4 48.4 50.4	2.0 2.0 2.0 2.0 2.0 2.0 2.0 2.0 2.0 2.0 2.0 2.0 2.0 2.0 1.6	2.74 2.74 2.67 2.67 2.71 2.71 2.71 2.73 2.73 2.73 2.73 2.65 2.65 2.65	73 77 35 33 103 80 106 54 35 36 27 156 156 29 40	24 27 28 27 24 23 21 27 21 22 24 28 26 26 26	2.10 2.61 2.05 2.40 2.35 2.06 1.91 2.57 1.89 2.45 2.63 3.84 2.87 2.93 3.17

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni %	Co ppm	Mg %
52.0	53.7	100	FAULT GOUGE Some intact pieces of andesite exist (~8cm) with milky-white calcareous stringers throughout.	46717	52.0	53.7	1.7	n/a	676	36	2.04
53.7	75.2	100	ANDESITE Hard, grey, compact, somewhat fragmented, weakly magnetic.	46718 46719 46720 46721 46722 46723 46724 46725 46726 46727 46728	53.7 55.7 57.7 59.7 61.7 63.7 65.7 67.7 69.7 71.7 73.7	55.7 57.7 59.7 61.7 63.7 65.7 67.7 69.7 71.7 73.7 75.2	2.0 2.0 2.0 2.0 2.0 2.0 2.0 2.0 2.0 2.0 2.0	2.68 2.68 2.74 2.74 2.72 2.72 2.72 2.69 2.69 2.69 2.91	59 223 680 34 65 58 28 72 272 146 55	21 27 52 17 26 20 20 25 28 20 21	2.38 3.40 4.02 1.66 2.75 2.51 1.80 2.18 3.13 1.50 2.34
75.2	86.0	100	SERPENTINITE Magnetic, thick magnetite webs throughout littered with fractures, stringers and blebs that are healed with calcareous material. Upper contact is sharp and 90° to c.a.	46729 46730 46731 46732 46733 46734 46735	75.2 76.7 78.2 79.7 81.2 82.7 84.2	76.7 78.2 79.7 81.2 82.7 84.2 86.0	1.5 1.5 1.5 1.5 1.5 1.5 1.8	2.76 2.76 2.63 2.63 2.63 2.75 2.75	2020 1846 1055 1935 1886 1048 1671	103 92 72 91 93 69 88	23.25 22.37 15.03 21.69 20.90 17.06 20.03
86.0	92.4	90	SERPENTINIZED ANDESITE Milky-white to dark-grey, aphanitic, fragmented, weakly magnetic.	46736 46737 46738	86.0 88.0 90.0	88.0 90.0 92.4	2.0 2.0 2.4	2.91 2.78 2.78	880 1054 906	48 59 61	7.71 6.81 6.53
92.4	94.6	100	AUGITE PORPHYRY Dark grey groundmass, with augite phenocrysts up to 8mm long, hard, non-magnetic, upper & lower contacts are gradational.	46739 46740	92.4 93.6	93.6 94.6	1.2 1.0	2.84 2.84	48 402	31 36	4.17 5.51
94.6	98.8	100	SERPENTINITE Magnetic, thick magnetite webs throughout littered with fractures, stringers and blebs that are healed with calcareous material. Somewhat fragmented.	46741 46742 46743	94.6 96.1 97.6	96.1 97.6 98.8	1.5 1.5 1.2	2.86 2.86 2.86	1660 1777 1678	79 83 102	15.57 17.68 16.55
98.8	107.0	100	ANDESITE Hard, grey, compact, somewhat fragmented, weakly magnetic. (not sampled)	* * *	* * *	* * *	* * *	* * *			
107.0	109.4	100	SERPENTINIZED ANDESITE Milky-white to dark-grey, aphanitic, fragmented, weakly magnetic. (not sampled)	* * *	* * *	* * *	* * *	* * *			

END OF HOLE

DIAMOND DRILL HOLE RECORD

RECORD RIDGE SOUTH

DDH RRS08-45

DIP AND AZIMUTH TESTS			CORE SIZE: NQ	TOTAL DEPTH: 72.9m	DATE STARTED: October 8, 2008
DEPTH	ANGLE	AZIMUTH	HOLE ANGLE: - 90°	HOLE AZIMUTH °	DATE FINISHED: October 9, 2008
72.9m	-89.3°	336.9°	SECTION:	COLLAR ELEVATION: 1414.9m	ANALYSIS BY: Assayers Canada
			GRID LOCATION: 650S/ 1275W	RECOVERY:	LOGGED BY: H.K. & C.P.
			UTM (NAD 83): 5432239 N 434627 E	CLAIM: Frank Sr. 3	CORE STORED AT: Midnight camp

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm³)	Ni %	Co ppm	Mg %
0.0	5.8	50	SURFACE BOULDERS AND FAULT GOUGE								
5.8	18.0	100	SERPENTINITE Dark-grey, magnetic, fragmented with milky-white and rusted appearance, contains some magnetite webs at random intervals.	46744	5.8	7.3	1.5	2.89	1576	91	16.68
				46745	7.3	8.8	1.5	2.89	1366	82	15.65
				46746	8.8	10.3	1.5	2.89	1934	88	18.72
				46747	10.3	11.8	1.5	2.89	1453	83	15.99
				46748	11.8	13.3	1.5	2.89	1437	104	15.52
				46749	13.3	14.8	1.5	2.89	1505	89	16.35
				46750	14.8	16.3	1.5	2.89	2144	127	18.83
				46751	16.3	18.0	1.7	2.89	1820	105	17.18
18.0	26.9	100	ANDESITE Grey, hard, compact, aphanitic, magnetic, calcareous-lined fractures run through the c.a. at random intervals.	46752	18.0	20.0	2.0	2.78	31	24	2.80
				46753	20.0	22.0	2.0	2.78	235	28	2.43
				46754	22.0	24.0	2.0	2.78	13	25	1.98
				46755	24.0	26.0	2.0	2.76	27	23	1.37
26.9	30.6	100	BRECCIA Milky-white groundmass with angular to sub-angular andesite clasts up to 30mm in length, upper and lower contacts are gradational.	46756	26.0	28.0	2.0	2.9	291	30	2.84
				46757	28.0	30.0	2.0	2.9	688	40	4.56
30.6	72.9	100	ANDESITE Grey, hard, compact, aphanitic, magnetic, calcareous-lined fractures run through the c.a. at random intervals.	46758	30.0	32.0	2.0	2.81	183	27	2.18
				46759	32.0	34.0	2.0	2.81	39	24	1.64
				46760	34.0	36.0	2.0	2.81	15	21	1.42
				46761	36.0	38.0	2.0	2.83	328	33	4.62
				46762	38.0	40.0	2.0	2.83	20	24	1.47
				46763	40.0	42.0	2.0	2.83	10	24	1.54
				46764	42.0	44.0	2.0	2.85	14	25	1.78
				46765	44.0	46.0	2.0	2.85	57	28	2.28
				46766	46.0	48.0	2.0	2.85	46	28	2.18
				46767	48.0	50.0	2.0	2.87	141	37	3.51
				46768	50.0	52.0	2.0	2.87	8	25	1.60
				46769	52.0	54.0	2.0	2.84	10	25	1.52
				46770	54.0	56.0	2.0	2.84	10	23	1.40

DEPTH (meters) FROM TO		Recover %	Description	Sample No.	FROM m	TO m	Length m	P (g/cm ³)	Ni %	Co ppm	Mg %
				46771	56.0	58.0	2.0	2.84	6	26	1.71
				46772	58.0	60.0	2.0	2.86	7	23	1.52
				46773	60.0	62.0	2.0	2.86	18	25	1.32
				46774	62.0	64.0	2.0	2.79	8	24	1.40
				46775	64.0	66.0	2.0	2.79	12	23	1.07
				46776	66.0	68.0	2.0	2.79	15	22	1.15
				46777	68.0	70.0	2.0	2.73	8	31	1.95
				46778	70.0	71.5	1.5	2.73	5	27	1.52
				46779	71.5	72.9	1.4	2.73	8	26	1.55

END OF HOLE

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2181RJ

Date : Nov-19-08

Why Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

Multi-Element ICP-AES Analysis

Aqua Regia Digestion

Sample Number	Ag ppm	Al %	As ppm	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	Hg ppm	K %	La ppm	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	S %	Sb ppm	Sc ppm	Sr ppm	Th ppm	Ti %	Tl ppm	U ppm	V ppm	W ppm	Zn ppm	Zr ppm
43462	<0.2	3.25	<5	246	<0.5	32	0.56	1	24	264	45	4.21	<1	0.66	<10	6.10	372	<2	0.05	426	724	<2	0.03	8	11	174	<5	0.10	<10	<10	117	<10	18	2
43463	<0.2	4.14	<5	193	<0.5	47	0.46	2	44	384	148	5.18	<1	0.41	<10	12.28	824	<2	0.01	851	624	<2	0.13	9	9	24	<5	0.05	<10	<10	102	<10	23	2
43464	<0.2	5.37	<5	243	<0.5	34	0.60	2	20	17	91	6.15	<1	1.64	<10	6.08	686	<2	0.09	27	1072	19	0.37	<5	16	106	<5	0.12	<10	<10	210	<10	62	3
43494	<0.2	5.42	<5	119	<0.5	43	0.39	2	23	51	38	6.82	<1	0.63	<10	8.43	1549	<2	0.04	62	1195	29	0.92	<5	18	26	<5	0.17	<10	<10	241	<10	125	3
43495	0.2	3.95	<5	68	<0.5	30	1.04	2	26	11	33	5.87	<1	0.32	<10	4.73	3046	2	0.05	30	1111	92	1.45	<5	14	78	<5	0.19	<10	<10	180	<10	207	3
43496	<0.2	3.77	<5	29	<0.5	33	1.02	2	31	190	69	6.11	<1	0.11	<10	6.89	2569	3	0.03	306	883	30	0.88	6	15	27	<5	0.16	<10	<10	176	<10	156	3
43500	<0.2	5.84	<5	343	<0.5	44	0.52	1	36	167	<1	5.73	<1	1.09	<10	10.66	677	<2	0.06	377	968	<2	0.04	8	15	107	<5	0.14	<10	<10	176	<10	29	3
43502	<0.2	4.47	<5	161	<0.5	36	0.92	1	31	101	10	4.45	<1	1.02	<10	6.96	515	<2	0.06	375	1074	<2	0.04	<5	9	161	<5	0.10	<10	<10	136	<10	38	3
43503	<0.2	4.34	<5	533	<0.5	31	0.33	1	17	127	11	4.67	<1	2.21	<10	6.17	452	<2	0.09	163	1091	<2	<0.01	7	9	72	<5	0.10	<10	<10	116	<10	23	2
43504	<0.2	2.37	<5	231	<0.5	20	0.32	1	12	19	<1	3.06	1	1.05	<10	2.65	286	<2	0.07	34	843	<2	0.02	<5	7	154	<5	0.11	<10	<10	81	<10	19	2
43505	<0.2	3.15	<5	119	<0.5	37	0.14	1	40	440	13	3.38	<1	0.48	<10	6.69	563	2	0.02	556	423	<2	0.22	10	5	16	<5	0.02	<10	<10	50	<10	15	1
43517	<0.2	6.29	<5	570	<0.5	30	1.29	2	31	20	208	7.27	<1	2.70	<10	6.84	767	<2	0.14	29	1043	<2	<0.01	5	25	184	<5	0.27	<10	<10	312	<10	41	3
43525	<0.2	2.12	<5	887	0.9	16	2.30	1	25	212	5	4.08	<1	1.39	24	4.18	609	<2	0.08	187	3403	9	0.04	11	3	165	9	0.34	<10	24	97	<10	60	25
43551	<0.2	5.06	<5	148	<0.5	36	1.52	1	16	300	<1	4.12	<1	0.69	<10	9.14	842	<2	0.04	164	982	22	<0.01	10	11	42	<5	0.10	<10	<10	148	<10	53	2
43552	<0.2	3.41	<5	124	<0.5	34	1.81	1	52	771	57	4.36	<1	0.44	<10	7.34	604	<2	0.04	979	524	9	0.09	19	5	42	<5	0.07	<10	<10	81	<10	36	2
43558	<0.2	5.20	<5	55	<0.5	34	2.71	2	32	30	68	6.33	<1	0.38	<10	7.03	2192	<2	0.08	59	1012	44	0.36	5	17	69	<5	0.16	<10	<10	235	<10	101	3
43559	0.8	4.97	<5	40	<0.5	31	1.68	2	36	88	145	6.85	<1	0.28	<10	5.47	5597	8	0.07	157	1018	51	0.16	5	17	49	<5	0.22	<10	<10	241	<10	319	4
43560	<0.2	4.85	<5	96	<0.5	37	1.45	2	36	84	33	7.02	<1	0.49	<10	6.28	2864	<2	0.06	175	987	75	0.04	8	23	54	<5	0.21	<10	<10	255	<10	183	3
43568	<0.2	0.78	<5	16	<0.5	47	0.71	3	73	441	<1	5.23	<1	0.01	<10	9.47	824	<2	0.01	1226	78	7	0.05	15	5	34	<5	0.02	<10	<10	28	<10	18	2
43569	<0.2	8.72	<5	698	<0.5	45	1.78	2	27	1	204	7.77	<1	1.55	<10	11.34	1688	<2	0.03	19	1564	2	0.02	<5	25	221	<5	0.14	<10	<10	289	<10	71	4
43587	<0.2	3.74	<5	141	<0.5	33	0.97	1	24	264	<1	4.33	<1	0.86	<10	6.63	477	<2	0.08	310	890	<2	0.01	5	6	49	<5	0.13	<10	<10	128	<10	24	3
Duplicates:																																		
43462	<0.2	3.31	<5	244	<0.5	34	0.57	1	24	272	45	4.28	<1	0.67	<10	6.22	382	<2	0.06	432	736	<2	0.03	5	11	177	<5	0.10	<10	<10	119	<10	18	2
43504	<0.2	2.41	<5	234	<0.5	21	0.32	1	12	19	<1	3.11	<1	1.06	<10	2.68	291	<2	0.07	35	843	<2	0.01	<5	7	154	<5	0.11	<10	<10	82	<10	19	2
43569	<0.2	8.82	<5	690	<0.5	48	1.78	2	29	1	216	7.79	<1	1.58	<10	11.60	1695	<2	0.03	19	1572	<2	0.01	<5	25	216	<5	0.15	<10	<10	290	<10	72	4
Standards:																																		
Blank	<0.2	<0.01	<5	<10	<0.5	<5	<0.01	<1	<1	<1	1	<0.01	<1	<0.01	<10	<0.01	<5	<2	<0.01	<1	<10	<2	<0.01	<5	<1	<1	<5	<0.01	<10	<10	<1	<10	<1	<1
ICP-2	0.4	1.69	51	183	0.5	22	4.15	4	80	186	1228	6.29	2	0.24	18	1.55	1753	5	0.03	98	1134	64	2.07	7	8	479	<5	0.02	<10	18	119	<10	316	10

A .5 gm sample is digested with 5 ml 3:1 HCl/HNO3 at 95°C for 2 hours and diluted to 25ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2217RJ

Date : Nov-20-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

Multi-Element ICP-AES Analysis

Aqua Regia Digestion

Sample Number	Ag ppm	Al %	As ppm	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	Hg ppm	K %	La ppm	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	S %	Sb ppm	Sc ppm	Sr ppm	Th ppm	Ti %	Tl ppm	U ppm	V ppm	W ppm	Zn ppm	Zr ppm
43647	4.4	4.86	<5	73	0.9	<5	1.88	11	32	125	39	7.58	<1	0.26	39	5.69	5672	<2	0.03	104	3042	6808	0.25	<5	8	135	17	0.13	<10	<10	133	11	1851	13
43648	<0.2	2.49	<5	214	1.5	<5	2.18	2	24	82	10	4.81	<1	0.68	46	2.17	2021	<2	0.09	29	3041	264	0.05	<5	7	167	19	0.28	<10	<10	112	<10	287	17
43649	<0.2	2.17	<5	238	1.6	<5	1.70	1	22	83	2	4.45	<1	0.79	44	2.18	853	2	0.09	26	2899	83	0.07	<5	6	126	18	0.26	<10	<10	108	<10	105	17
43650	<0.2	3.05	<5	201	1.7	<5	0.88	4	22	78	3	5.10	<1	0.82	49	3.56	2237	<2	0.06	23	3007	540	0.10	<5	8	83	18	0.18	<10	<10	115	<10	577	11
43651	0.9	3.75	<5	48	1.3	<5	2.53	11	41	213	24	6.68	<1	0.14	38	5.76	5333	<2	0.02	437	2382	1032	0.36	<5	7	165	16	0.07	<10	<10	88	12	2073	8
43652	<0.2	3.19	<5	87	1.0	<5	2.19	2	21	70	<1	6.31	<1	0.27	48	2.66	4107	<2	0.04	38	2977	249	0.19	<5	7	142	21	0.11	<10	<10	101	<10	346	10
43653	<0.2	4.47	<5	48	1.0	<5	3.09	2	23	83	<1	8.26	<1	0.14	60	3.78	5973	<2	0.03	54	3090	45	0.16	<5	7	189	21	0.07	<10	<10	115	<10	265	13
43654	<0.2	4.46	<5	88	1.2	<5	1.40	3	24	82	<1	7.88	<1	0.32	62	4.17	5222	<2	0.04	41	3278	224	0.15	<5	7	107	22	0.11	<10	<10	120	<10	394	14
43676	<0.2	7.00	<5	<10	<0.5	<5	0.28	1	24	11	<1	4.32	<1	<0.01	<10	11.94	1051	<2	<0.01	43	1224	<2	<0.01	<5	25	28	<5	0.03	<10	<10	204	<10	49	3
43777	<0.2	1.88	<5	<10	<0.5	7	1.53	1	58	370	6	4.28	<1	0.01	<10	10.82	863	<2	<0.01	1165	497	7	0.19	15	11	135	<5	0.01	<10	<10	61	<10	25	2
43704	<0.2	2.01	20	258	0.5	<5	1.25	1	52	394	<1	3.82	<1	0.82	<10	6.72	698	<2	0.17	892	848	20	0.54	9	4	171	5	0.13	<10	<10	64	<10	35	3
43705	<0.2	3.77	<5	245	1.2	<5	1.87	1	22	102	<1	4.24	<1	1.46	17	1.72	420	<2	0.52	17	1915	15	0.28	<5	6	346	9	0.28	<10	<10	122	<10	47	6
Duplicates:																																		
43647	4.2	4.62	<5	69	0.8	<5	1.78	11	30	118	35	7.28	<1	0.25	34	5.43	5417	<2	0.02	99	2898	6448	0.23	<5	8	124	15	0.11	<10	<10	125	10	1765	11
43777	<0.2	1.91	<5	<10	<0.5	8	1.52	1	58	373	6	4.28	<1	0.01	<10	10.78	863	<2	<0.01	1174	496	7	0.19	12	11	135	<5	0.01	<10	<10	62	<10	25	2
Standards:																																		
Blank	<0.2	<0.01	<5	<10	<0.5	<5	<0.01	<1	<1	<1	3	<0.01	<1	<0.01	<10	<0.01	<5	<2	<0.01	<1	<10	<2	<0.01	<5	<1	<1	<5	<0.01	<10	<10	<1	<10	<1	<1
ICP-2	<0.2	1.51	49	158	0.5	<5	3.80	3	81	175	1170	6.12	1	0.21	18	1.50	1706	5	0.02	97	1105	66	1.94	<5	7	441	7	0.01	<10	<10	113	<10	288	11

A .5 gm sample is digested with 5 ml 3:1 HCl/HNO3 at 95°C for 2 hours and diluted to 25ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2333RJ

Date : Jul-11-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

Multi-Element ICP-AES Analysis

Aqua Regia Digestion

Sample Number	Ag ppm	Al %	As ppm	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	Hg ppm	K %	La ppm	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	S %	Sb ppm	Sc ppm	Sr ppm	Th ppm	Ti %	Tl ppm	U ppm	V ppm	W ppm	Zn ppm	Zr ppm
43801	<0.2	2.70	23	478	1.4	<5	3.53	3	60	447	10	5.38	<1	0.56	19	10.57	1765	<2	0.02	805	2596	227	0.05	9	11	276	7	0.19	<10	<10	94	<10	184	23
43802	0.3	5.17	<5	956	2.2	<5	3.72	9	50	339	35	6.16	<1	1.26	37	10.82	2243	<2	0.03	342	4098	823	0.02	<5	18	137	11	0.31	<10	<10	150	<10	578	27
43817	<0.2	1.73	7	142	1.1	<5	1.36	1	40	252	30	4.12	1	0.89	21	5.62	759	<2	0.06	432	2328	19	0.11	<5	5	<1	8	0.20	<10	<10	82	<10	67	6
43818	<0.2	2.10	<5	97	1.5	<5	2.03	2	21	75	37	4.31	<1	0.60	42	1.85	1529	2	0.08	21	3186	130	0.14	<5	5	31	16	0.21	<10	<10	98	<10	276	12
43819	<0.2	1.92	<5	110	1.5	<5	1.76	1	22	102	23	4.08	<1	0.63	30	2.02	623	<2	0.07	26	3263	10	0.08	<5	5	12	13	0.25	<10	<10	103	<10	64	12
43820	<0.2	2.41	<5	72	1.0	<5	2.24	3	21	96	15	5.16	<1	0.25	39	2.14	2485	<2	0.04	25	3114	340	0.15	<5	6	<1	15	0.15	<10	<10	103	<10	606	9
43821	<0.2	1.94	<5	168	1.3	<5	1.66	1	22	114	16	4.03	<1	0.59	30	2.16	525	<2	0.08	28	3278	7	0.01	<5	4	<1	14	0.25	<10	<10	101	<10	66	10
43824	<0.2	1.44	<5	69	0.9	<5	1.47	1	21	118	18	3.41	<1	0.28	27	1.73	547	<2	0.06	81	2922	14	0.03	<5	2	41	9	0.18	<10	<10	77	<10	70	7
43825	1.6	1.51	<5	66	0.9	<5	1.74	3	19	92	62	3.49	<1	0.17	29	1.51	904	<2	0.07	20	2948	116	0.06	<5	3	76	9	0.19	<10	<10	82	<10	585	8
43826	<0.2	1.98	<5	123	0.9	<5	1.67	2	20	100	35	4.31	<1	0.22	30	1.70	1926	<2	0.07	24	2849	114	0.06	<5	4	10	8	0.17	<10	<10	89	<10	395	8
43827	<0.2	1.86	<5	120	1.0	<5	1.96	1	21	99	72	4.18	<1	0.20	34	1.56	1397	<2	0.09	23	2917	25	0.11	<5	4	34	11	0.22	<10	<10	93	<10	159	9
43828	4.8	2.92	<5	79	1.0	17	2.38	4	26	105	470	6.22	<1	0.25	34	2.33	3214	<2	0.05	23	2956	330	0.23	<5	7	<1	12	0.12	<10	<10	113	<10	729	8
43829	2.8	3.16	<5	52	0.9	6	2.59	8	32	116	158	6.63	<1	0.20	37	2.46	3648	<2	0.04	27	3145	327	0.38	<5	6	<1	12	0.12	<10	<10	110	<10	1775	9
43830	<0.2	2.03	<5	247	1.4	<5	2.10	1	25	169	7	3.78	<1	0.91	23	2.29	1686	<2	0.06	57	2941	58	0.02	<5	4	11	9	0.27	<10	<10	92	<10	297	10
43831	<0.2	1.95	<5	116	1.4	<5	1.81	1	25	168	10	3.58	<1	1.09	22	2.22	1437	<2	0.07	58	2945	77	0.02	<5	3	7	10	0.30	<10	<10	88	<10	243	12
43869	2.5	3.82	<5	48	0.9	<5	1.48	7	29	178	212	7.47	<1	0.28	26	3.33	4673	<2	0.03	48	2766	667	0.45	<5	11	<1	8	0.11	<10	<10	127	<10	1388	8
43870	48.6	3.77	<5	38	0.7	101	1.31	30	43	80	1826	7.98	<1	0.24	15	2.93	5461	<2	0.03	63	2623	3692	1.44	<5	8	<1	<5	0.08	<10	<10	121	<10	6167	7
43871	<0.2	2.14	<5	55	0.9	<5	3.34	1	22	191	121	3.68	<1	0.31	17	2.54	1993	<2	0.04	43	2693	68	0.14	<5	8	226	5	0.16	<10	<10	98	<10	158	6
43872	<0.2	2.81	<5	67	0.9	<5	3.50	2	25	110	132	4.79	<1	0.30	19	2.90	2829	<2	0.04	40	2326	250	0.26	<5	9	170	7	0.11	<10	<10	114	<10	348	5
43873	1.0	2.95	<5	79	1.1	<5	2.48	8	23	75	58	5.44	<1	0.51	17	2.43	3021	<2	0.07	13	2147	449	0.19	<5	8	<1	5	0.16	<10	<10	124	<10	1673	6
43874	2.4	3.24	<5	64	1.2	<5	2.84	21	24	80	103	5.64	<1	0.49	21	2.58	3375	<2	0.09	13	2137	1309	0.42	<5	9	<1	8	0.16	<10	<10	125	<10	4221	7
43875	<0.2	3.43	<5	226	1.5	<5	1.97	2	23	76	2	4.77	<1	1.19	15	2.67	2332	<2	0.19	15	2103	92	0.03	<5	8	<1	7	0.26	<10	<10	124	<10	434	6
43876	4.0	4.37	<5	323	1.2	7	1.16	3	58	374	506	7.62	1	1.22	10	4.62	2767	<2	0.17	411	1595	146	1.16	5	7	<1	<5	0.20	<10	<10	120	<10	464	7
43877	<0.2	4.04	<5	350	1.5	<5	1.06	2	26	104	20	5.87	<1	1.23	13	3.27	2999	<2	0.20	55	2060	96	0.14	<5	9	<1	<5	0.26	<10	<10	128	<10	474	7
43878	0.6	3.82	<5	174	1.7	<5	2.04	3	25	89	30	5.46	<1	1.19	17	2.44	2125	<2	0.32	9	2387	85	0.06	<5	7	239	5	0.32	<10	<10	133	<10	527	7
43879	<0.2	3.81	<5	167	1.8	<5	2.14	2	24	92	1	4.81	1	1.37	17	2.08	1226	<2	0.41	9	2473	119	0.03	<5	5	324	7	0.35	<10	<10	135	<10	177	8
43880	<0.2	3.46	<5	174	1.6	<5	2.17	1	21	79	2	4.03	<1	1.25	15	1.80	634	<2	0.41	8	2094	<2	0.06	<5	5	298	5	0.29	<10	<10	116	<10	76	7
43881	<0.2	3.67	<5	206	1.6	<5	2.09	1	21	78	<1	4.10	<1	1.42	12	2.08	784	<2	0.41	15	1971	14	0.05	<5	6	321	<5	0.28	<10	<10	117	<10	84	6
43882	<0.2	3.11	12	170	1.5	<5	1.79	1	20	82	1	3.96	<1	1.25	14	1.63	462	7	0.39	9	2102	2	0.02	<5	4	280	5	0.29	<10	<10	116	<10	72	6
43883	0.6	3.11	<5	188	1.3	<5	1.87	5	23	95	32	4.58	1	1.06	12	2.20	1449	<2	0.26	43	1918	53	0.16	<5	6	216	<5	0.26	<10	<10	113	<10	985	6

A .5 gm sample is digested with 5 ml 3:1 HCl/HNO3 at 95°C for 2 hours and diluted to 25ml.

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2333RJ

Date : Jul-11-08

Multi-Element ICP-AES Analysis

Aqua Regia Digestion

Sample Number	Ag ppm	Al %	As ppm	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	Hg ppm	K %	La ppm	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	S %	Sb ppm	Sc ppm	Sr ppm	Th ppm	Ti %	Tl ppm	U ppm	V ppm	W ppm	Zn ppm	Zr ppm
43884	1.6	3.05	<5	298	1.4	<5	1.83	6	30	53	117	5.83	1	0.92	19	2.19	2264	<2	0.16	10	2522	127	0.34	<5	7	177	6	0.28	<10	<10	134	<10	1066	6
43885	<0.2	2.83	10	857	1.7	<5	1.91	1	30	108	11	4.35	<1	1.59	23	2.12	594	<2	0.27	39	3465	8	0.05	<5	4	421	6	0.35	<10	<10	119	<10	92	6
43886	<0.2	2.57	9	818	1.3	<5	1.91	1	32	136	14	5.21	1	1.50	21	2.58	1499	<2	0.11	62	3459	40	0.12	<5	5	212	5	0.33	<10	<10	119	<10	156	7
43887	3.4	3.33	<5	80	0.9	6	3.11	8	31	143	69	7.34	<1	0.34	22	2.93	3697	<2	0.06	28	2365	657	0.31	<5	10	219	6	0.14	<10	<10	135	<10	1512	8
Duplicates:																																		
43801	<0.2	2.90	25	515	1.4	<5	3.78	3	64	474	10	5.77	<1	0.60	20	11.29	1887	<2	0.02	859	2783	248	0.05	10	12	204	7	0.19	<10	<10	100	<10	199	22
43826	<0.2	2.12	<5	136	1.0	<5	1.80	2	21	107	38	4.53	<1	0.24	33	1.81	2031	<2	0.08	26	3035	123	0.06	<5	5	<1	9	0.20	<10	<10	97	<10	419	9
43873	1.0	2.92	<5	78	1.1	<5	2.41	8	22	73	58	5.28	<1	0.50	17	2.40	2936	<2	0.07	12	2102	435	0.19	<5	8	<1	5	0.16	<10	<10	122	<10	1635	6
43878	0.5	3.28	<5	150	1.5	<5	1.78	3	21	75	23	4.66	1	1.00	15	2.09	1818	<2	0.28	9	2026	78	0.05	<5	6	206	<5	0.28	<10	<10	114	<10	451	6
43887	3.6	3.24	<5	59	0.9	6	3.06	8	30	140	62	7.17	1	0.30	22	2.85	3649	<2	0.06	27	2247	662	0.31	<5	10	213	6	0.13	<10	<10	131	<10	1436	7
Standards:																																		
Blank	<0.2	<0.01	<5	<10	<0.5	<5	<0.01	<1	<1	<1	<1	<0.01	1	<0.01	<10	<0.01	<5	<2	0.01	<1	<10	<2	<0.01	<5	<1	<1	<5	<0.01	<10	<10	<1	<10	1	<1
ICP-2	0.5	1.45	55	167	0.5	<5	4.00	3	83	176	1145	5.88	1	0.19	17	1.48	1675	5	0.02	98	1208	61	1.98	<5	7	419	<5	0.01	<10	<10	113	<10	303	11

A .5 gm sample is digested with 5 ml 3:1 HCl/HNO3 at 95°C for 2 hours and diluted to 25ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2537RJ

Date : Nov-25-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

Multi-Element ICP-AES Analysis

Aqua Regia Digestion

Sample Number	Ag ppm	Al %	As ppm	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	Hg ppm	K %	La ppm	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	S %	Sb ppm	Sc ppm	Sr ppm	Th ppm	Ti %	Tl ppm	U ppm	V ppm	W ppm	Zn ppm	Zr ppm
44414	0.2	1.59	12	12	<0.5	<5	2.98	<1	86	707	16	4.79	<1	0.01	<10	12.68	989	<2	0.02	1311	283	142	1.19	<5	10	214	<5	0.03	<10	<10	53	<10	40	2
44415	<0.2	4.19	9	<10	<0.5	<5	1.38	<1	54	350	41	4.88	<1	0.01	<10	>15.00	936	<2	0.01	754	605	54	0.45	<5	20	80	<5	0.07	<10	<10	119	<10	49	3
44423	<0.2	5.46	<5	192	1.1	<5	2.95	<1	42	80	67	5.12	<1	1.00	<10	8.52	946	<2	0.22	213	924	14	0.25	<5	17	179	<5	0.22	<10	<10	203	<10	63	5
44424	<0.2	4.20	<5	229	1.8	<5	2.30	<1	39	36	39	5.22	<1	1.77	<10	3.29	798	<2	0.32	32	967	9	0.07	<5	16	252	<5	0.37	<10	<10	226	<10	75	6
44425	<0.2	4.16	<5	245	1.7	<5	2.69	<1	37	36	45	5.14	<1	1.70	<10	3.00	734	<2	0.36	24	932	10	0.09	<5	21	244	<5	0.34	<10	<10	216	<10	64	7
44426	<0.2	5.28	<5	283	1.9	<5	3.52	<1	40	31	43	5.93	<1	2.09	<10	3.35	891	<2	0.46	28	1027	17	0.14	<5	27	299	<5	0.38	<10	<10	269	<10	68	6
44427	<0.2	5.73	<5	449	1.6	<5	2.86	<1	40	51	49	6.50	<1	2.51	<10	4.07	797	<2	0.32	46	1207	33	0.35	<5	24	261	<5	0.32	<10	<10	280	<10	74	6
44428	<0.2	3.13	<5	132	1.3	<5	2.38	<1	31	34	32	4.64	<1	1.15	<10	2.66	787	<2	0.16	26	1282	11	0.08	<5	13	110	<5	0.28	<10	<10	148	<10	106	6
44459	<0.2	5.20	<5	242	0.9	<5	1.85	<1	58	329	2	4.87	<1	1.27	<10	7.65	842	<2	0.11	546	880	10	0.09	<5	23	169	<5	0.20	<10	<10	217	<10	54	3
44494	<0.2	4.92	<5	280	1.0	<5	0.60	<1	25	58	7	4.95	<1	1.04	<10	7.10	652	<2	0.05	72	936	8	0.66	<5	17	71	<5	0.12	<10	<10	193	<10	67	3
44495	<0.2	4.06	<5	149	0.8	<5	0.61	<1	28	187	24	4.36	<1	0.68	<10	6.59	533	<2	0.06	219	948	35	0.10	<5	21	52	<5	0.10	<10	<10	169	<10	65	2
44500	<0.2	4.72	<5	204	1.4	<5	2.77	<1	30	54	33	4.54	<1	1.11	<10	3.76	955	<2	0.45	50	1212	336	0.21	<5	10	468	<5	0.27	<10	<10	124	<10	200	5
Duplicates:																																		
*DUP 01	<0.2	1.59	13	11	<0.5	<5	2.84	<1	80	691	15	4.54	<1	0.01	<10	12.22	957	<2	0.01	1242	268	141	1.10	<5	10	206	<5	0.03	<10	<10	52	<10	34	2
*DUP 10	<0.2	4.86	<5	269	1.0	<5	0.59	<1	25	54	7	4.93	<1	1.02	<10	7.00	643	<2	0.05	71	918	8	0.66	<5	16	70	<5	0.11	<10	<10	185	<10	65	3
Standards:																																		
Blank	<0.2	<0.01	<5	<10	<0.5	<5	<0.01	<1	<1	<1	<1	<0.01	<1	<0.01	<10	<0.01	<5	<2	0.01	<1	<10	<2	<0.01	<5	<1	<1	<5	<0.01	<10	<10	<1	<10	<1	<1
ICP-2	0.4	1.80	62	99	0.6	<5	4.23	1	88	197	1237	6.17	<1	0.26	18	1.70	1761	7	0.03	102	1453	69	2.18	<5	8	525	<5	0.02	<10	<10	127	<10	321	11

A .5 gm sample is digested with 5 ml 3:1 HCl/HNO3 at 95°C for 2 hours and diluted to 25ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2560RJ

Date : Nov-25-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

Multi-Element ICP-AES Analysis

Aqua Regia Digestion

Sample Number	Ag ppm	Al %	As ppm	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	Hg ppm	K %	La ppm	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	S %	Sb ppm	Sc ppm	Sr ppm	Th ppm	Ti %	Tl ppm	U ppm	V ppm	W ppm	Zn ppm	Zr ppm
44501	<0.2	2.82	<5	231	1.0	<5	1.56	<1	23	67	54	2.99	1	0.73	<10	3.37	559	<2	0.03	77	1734	22	0.06	<5	6	73	<5	0.18	<10	<10	71	<10	66	7
44502	<0.2	1.62	<5	232	1.6	<5	1.71	<1	33	244	104	2.96	1	0.41	18	3.28	521	<2	0.05	303	2035	25	0.05	<5	3	112	7	0.23	<10	<10	60	<10	46	16
44507	0.3	5.12	<5	178	1.0	<5	2.61	<1	52	261	90	5.26	1	0.86	<10	7.66	997	<2	0.03	386	813	5	0.04	6	14	145	<5	0.23	<10	<10	172	<10	52	4
44508	0.5	3.46	<5	81	0.5	<5	1.01	<1	28	183	139	2.67	<1	0.68	<10	5.50	618	<2	0.07	175	1246	15	0.01	<5	6	99	<5	0.11	<10	<10	78	<10	81	2
44570	<0.2	1.74	<5	321	1.6	<5	1.38	<1	26	135	83	3.13	<1	0.57	25	2.53	431	<2	0.04	120	2376	21	0.42	<5	2	137	10	0.29	<10	<10	75	<10	50	16
44571	<0.2	2.71	<5	169	1.4	<5	2.63	<1	37	324	57	3.98	<1	0.29	19	5.56	2306	2	0.03	320	2320	143	0.33	<5	6	187	7	0.20	<10	<10	85	<10	188	13
44572	<0.2	1.81	<5	421	1.6	<5	1.36	<1	28	157	84	3.18	<1	0.65	24	2.61	1032	2	0.05	135	2431	18	0.15	<5	4	183	9	0.30	<10	<10	86	<10	61	19
44573	<0.2	2.00	<5	489	2.1	<5	0.99	<1	30	193	46	3.61	<1	1.33	21	3.18	621	<2	0.05	83	2757	20	0.31	<5	5	150	9	0.37	<10	<10	113	<10	41	16
44574	<0.2	2.46	<5	353	1.7	<5	1.62	<1	32	222	36	3.91	<1	0.80	20	3.80	1665	<2	0.03	121	2641	24	0.24	<5	6	136	8	0.31	<10	<10	110	<10	107	13
44575	<0.2	1.65	<5	396	1.3	<5	1.55	<1	25	154	40	2.98	<1	0.64	21	2.36	873	<2	0.05	112	2200	19	0.11	<5	3	141	8	0.27	<10	<10	78	<10	60	15
44576	<0.2	1.45	<5	405	1.4	<5	1.29	<1	24	124	43	2.82	<1	0.70	22	1.99	498	<2	0.07	105	2051	10	0.07	<5	2	130	8	0.27	<10	<10	71	<10	38	16
44577	<0.2	1.56	<5	386	1.4	<5	1.03	<1	26	108	97	2.90	<1	0.64	21	2.20	475	2	0.08	126	1993	12	0.05	<5	2	149	7	0.28	<10	<10	70	<10	40	17
44578	<0.2	1.55	<5	453	1.5	<5	1.12	<1	26	123	85	3.03	<1	0.78	22	2.10	359	2	0.08	102	2074	13	0.04	<5	2	138	8	0.30	<10	<10	76	<10	31	18
44579	1.0	2.24	<5	354	1.6	<5	1.71	10	30	200	148	3.99	<1	0.53	20	3.17	1564	<2	0.04	140	2550	1507	0.15	<5	4	113	7	0.29	<10	<10	89	21	1560	14
44580	<0.2	2.23	<5	357	1.4	<5	1.11	<1	29	147	55	4.05	<1	0.68	20	2.87	1579	2	0.05	129	2405	34	0.14	<5	3	113	7	0.25	<10	<10	83	<10	142	14
44581	<0.2	1.78	<5	349	1.3	<5	1.75	<1	25	151	84	3.30	<1	0.57	19	2.61	962	<2	0.04	123	2109	52	0.05	<5	3	143	7	0.23	<10	<10	73	<10	95	14
44582	<0.2	1.62	<5	368	1.3	<5	1.41	<1	24	132	130	2.92	<1	0.77	19	2.55	462	<2	0.05	97	2209	23	0.05	<5	2	132	6	0.27	<10	<10	72	<10	46	15
44583	<0.2	1.01	17	169	1.1	<5	1.47	<1	58	197	87	3.82	<1	0.26	12	8.81	798	<2	0.04	778	2081	21	0.22	<5	3	82	<5	0.22	<10	<10	70	<10	39	8
44584	0.8	3.48	<5	123	1.4	<5	3.62	<1	33	188	94	5.29	<1	0.20	17	4.36	3100	<2	0.02	33	3248	659	0.19	<5	10	147	<5	0.27	<10	<10	140	<10	292	7
44597	0.4	5.48	<5	30	0.5	<5	2.97	<1	38	248	34	6.14	<1	0.11	29	6.52	5095	<2	0.01	114	3336	12	<0.01	<5	13	104	7	0.06	<10	18	136	<10	319	6
44598	<0.2	4.96	<5	44	0.6	<5	1.80	<1	40	24	35	6.35	1	0.26	<10	5.19	4650	<2	0.02	49	1265	22	0.01	<5	18	42	<5	0.13	<10	15	216	<10	293	4
44599	<0.2	2.88	<5	135	0.8	<5	1.64	<1	26	33	63	4.08	<1	1.05	<10	2.24	723	<2	0.22	24	1088	9	0.01	<5	8	107	<5	0.23	<10	<10	155	<10	58	6
44600	<0.2	4.16	<5	146	1.1	<5	2.46	<1	32	64	119	4.27	1	1.60	<10	2.87	916	<2	0.34	45	781	26	0.03	<5	12	181	<5	0.28	<10	<10	189	<10	78	6
Duplicates:																																		
44501	<0.2	3.02	<5	251	1.0	<5	1.72	<1	25	70	58	3.21	<1	0.79	10	3.56	600	<2	0.04	76	1673	32	0.06	<5	6	67	<5	0.20	<10	<10	75	<10	85	8
44575	<0.2	1.86	<5	421	1.4	<5	1.63	<1	26	159	39	3.12	<1	0.73	22	2.54	897	<2	0.06	109	2275	23	0.12	<5	3	143	8	0.29	<10	<10	82	<10	65	16
44597	0.7	6.10	<5	30	0.5	<5	2.93	<1	37	246	37	6.07	<1	0.15	31	7.02	5018	<2	0.01	110	3083	18	<0.01	<5	13	110	7	0.07	<10	20	138	<10	289	7
Standards:																																		
Blank	<0.2	<0.01	<5	<10	<0.5	<5	<0.01	<1	<1	4	1	<0.01	<1	<0.01	<10	<0.01	<5	<2	<0.01	<1	<10	<2	<0.01	<5	<1	<1	<5	<0.01	<10	<10	<1	<10	<1	<1
ICP-2	0.4	1.59	53	171	<0.5	<5	3.12	1	78	158	1271	4.85	1	0.22	16	1.41	1510	6	0.02	87	1269	70	2.18	<5	7	376	<5	0.02	<10	<10	102	<10	300	10

A .5 gm sample is digested with 5 ml 3:1 HCl/HNO3 at 95°C for 2 hours and diluted to 25ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2654RJ

Date : Nov-26-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

Multi-Element ICP-AES Analysis

Aqua Regia Digestion

Sample Number	Ag ppm	Al %	As ppm	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	Hg ppm	K %	La ppm	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	S %	Sb ppm	Sc ppm	Sr ppm	Th ppm	Ti %	Tl ppm	U ppm	V ppm	W ppm	Zn ppm	Zr ppm
44601	<0.2	3.45	<5	146	1.5	<5	2.88	<1	40	34	9	6.20	<1	0.96	<10	3.47	1876	<2	0.15	34	1137	18	0.10	<5	16	136	<5	0.32	<10	<10	249	<10	108	6
44602	<0.2	3.87	<5	110	1.6	<5	2.11	<1	41	40	2	6.40	<1	0.48	<10	4.84	1585	<2	0.09	36	1193	10	<0.01	<5	20	86	<5	0.33	<10	<10	276	<10	82	6
44603	<0.2	5.92	<5	<10	0.6	<5	5.56	<1	53	533	18	5.36	<1	0.02	<10	12.78	1327	<2	0.01	611	725	13	0.02	6	16	151	<5	0.13	<10	<10	185	<10	44	3
Duplicates:																																		
*DUP 01	<0.2	3.50	<5	148	1.6	<5	2.91	<1	40	35	4	6.27	1	0.99	<10	3.53	1910	<2	0.16	35	1145	18	0.10	<5	17	140	<5	0.33	<10	<10	255	<10	109	6
Standards:																																		
Blank	<0.2	<0.01	<5	<10	<0.5	<5	<0.01	<1	1	<1	<1	<0.01	<1	<0.01	<10	<0.01	<5	<2	0.01	<1	<10	<2	<0.01	<5	<1	<1	<5	<0.01	<10	<10	<1	<10	<1	<1
ICP-2	0.3	1.72	61	175	0.6	<5	4.06	1	90	196	1163	6.34	1	0.25	18	1.66	1741	7	0.03	94	1479	71	2.19	<5	8	487	<5	0.02	<10	<10	124	<10	325	11

A .5 gm sample is digested with 5 ml 3:1 HCl/HNO3 at 95°C for 2 hours and diluted to 25ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2665RJ

Date : Nov-26-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

Multi-Element ICP-AES Analysis

Aqua Regia Digestion

Sample Number	Ag ppm	Al %	As ppm	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	Hg ppm	K %	La ppm	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	S %	Sb ppm	Sc ppm	Sr ppm	Th ppm	Ti %	Tl ppm	U ppm	V ppm	W ppm	Zn ppm	Zr ppm
44705	<0.2	6.04	<5	209	0.8	<5	1.09	<1	35	43	<1	6.00	<1	1.32	<10	5.99	656	<2	0.15	54	1259	<2	<0.01	<5	21	98	<5	0.15	<10	<10	258	<10	51	3
44706	<0.2	4.63	<5	172	1.2	<5	2.14	<1	33	103	<1	5.37	<1	1.07	<10	4.16	647	<2	0.28	65	935	7	0.05	<5	15	162	<5	0.22	<10	<10	222	<10	62	3
44707	<0.2	4.86	<5	124	1.3	<5	2.14	<1	38	67	<1	5.86	<1	1.01	<10	4.30	1367	<2	0.26	49	1069	9	0.04	<5	19	144	<5	0.25	<10	<10	255	<10	96	4
44708	<0.2	4.76	<5	166	1.4	<5	2.31	<1	32	77	<1	5.03	<1	1.41	<10	3.20	480	<2	0.41	44	938	14	0.02	<5	12	136	<5	0.25	<10	<10	226	<10	46	3
44709	<0.2	4.90	<5	114	1.1	<5	1.80	<1	34	71	<1	4.95	<1	0.90	<10	4.69	599	<2	0.30	70	969	12	0.02	<5	16	112	<5	0.21	<10	<10	232	<10	61	3
44710	3.9	5.48	<5	17	0.7	<5	2.59	<1	55	158	45	6.10	<1	0.07	<10	7.42	2192	<2	0.03	306	1111	42	0.35	<5	14	120	<5	0.14	<10	<10	224	<10	236	4
44711	<0.2	5.32	<5	23	0.7	<5	2.83	<1	39	82	4	5.50	<1	0.10	<10	7.53	1164	<2	0.04	189	1168	14	0.02	<5	15	145	<5	0.16	<10	<10	218	<10	117	4
44712	<0.2	5.39	<5	41	1.1	<5	2.24	<1	46	84	<1	6.49	<1	0.17	<10	6.25	2706	<2	0.07	86	1123	12	0.20	<5	22	60	<5	0.20	<10	<10	258	<10	195	4
44713	<0.2	5.79	<5	11	0.9	<5	2.13	<1	42	42	<1	6.48	<1	0.03	<10	7.56	2862	<2	0.03	60	1265	10	0.09	<5	18	75	<5	0.17	<10	<10	228	<10	185	4
44714	<0.2	6.25	<5	<10	0.6	<5	1.21	<1	37	121	6	5.84	<1	0.01	<10	10.45	2076	<2	0.01	253	1000	6	0.02	<5	12	34	<5	0.10	<10	<10	194	<10	116	3
44794	<0.2	4.14	<5	78	1.4	<5	2.48	<1	30	50	4	4.94	<1	0.91	<10	2.63	1031	<2	0.25	28	1028	18	0.04	<5	12	202	<5	0.27	<10	<10	208	<10	82	4
44795	<0.2	4.98	<5	83	1.6	<5	2.99	<1	32	24	6	5.30	1	1.13	<10	3.38	563	<2	0.28	22	860	9	0.04	<5	14	214	<5	0.30	<10	<10	253	<10	49	4
44796	<0.2	4.67	<5	93	1.3	<5	3.31	<1	33	25	13	5.37	<1	0.99	<10	3.29	1656	<2	0.23	20	991	14	0.07	<5	14	155	<5	0.25	<10	<10	232	<10	92	4
44797	<0.2	4.54	<5	79	1.3	<5	3.82	<1	38	28	11	6.13	<1	0.54	<10	4.30	3289	<2	0.07	23	1116	17	0.07	<5	19	118	<5	0.25	<10	<10	247	<10	192	4
44798	0.7	5.48	<5	75	1.1	<5	1.78	<1	40	48	29	7.24	<1	0.49	<10	5.72	3896	<2	0.07	34	1178	211	0.03	<5	22	70	<5	0.22	<10	12	275	<10	362	4
44799	<0.2	3.65	<5	49	0.7	<5	2.83	<1	54	276	2	5.56	<1	0.13	<10	6.42	2493	<2	0.02	659	692	9	0.14	<5	15	81	<5	0.14	<10	<10	162	<10	103	3
44800	<0.2	0.86	16	<10	<0.5	<5	2.79	<1	73	362	7	4.59	<1	0.01	<10	8.41	992	<2	0.01	1517	199	8	0.29	<5	3	31	<5	0.02	<10	<10	32	<10	20	2
Duplicates:																																		
*DUP 01	<0.2	5.79	<5	202	0.7	<5	1.06	<1	34	40	<1	5.83	1	1.28	<10	5.84	635	<2	0.14	53	1206	<2	<0.01	<5	20	95	<5	0.13	<10	<10	249	<10	51	3
*DUP 10	<0.2	6.19	<5	<10	0.6	<5	1.19	<1	36	119	5	5.70	<1	0.01	<10	10.36	2046	<2	0.01	248	983	5	0.02	<5	12	34	<5	0.10	<10	<10	192	<10	113	3
Standards:																																		
Blank	<0.2	<0.01	<5	<10	<0.5	<5	<0.01	<1	<1	<1	1	<0.01	<1	<0.01	<10	<0.01	<5	<2	<0.01	<1	<10	<2	<0.01	<5	<1	<1	<5	<0.01	<10	<10	<1	<10	<1	<1
ICP-2	0.4	1.63	56	221	0.5	<5	3.82	1	83	183	1141	6.00	1	0.23	17	1.57	1651	6	0.03	98	1369	66	2.03	<5	8	452	<5	0.02	<10	<10	117	<10	300	11

A .5 gm sample is digested with 5 ml 3:1 HCl/HNO3 at 95°C for 2 hours and diluted to 25ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2805RJ

Date : Nov-28-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

Multi-Element ICP-AES Analysis

Aqua Regia Digestion

Sample Number	Ag ppm	Al %	As ppm	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	Hg ppm	K %	La ppm	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	S %	Sb ppm	Sc ppm	Sr ppm	Th ppm	Ti %	Tl ppm	U ppm	V ppm	W ppm	Zn ppm	Zr ppm
44801	<0.2	0.93	5	47	0.5	<5	3.12	1	58	452	11	3.92	<1	0.08	11	5.38	923	4	0.04	1074	1154	10	0.23	6	3	82	<5	0.15	<10	<10	44	<10	28	12
44802	<0.2	1.73	<5	350	<0.5	<5	2.53	<1	29	166	25	3.98	<1	0.51	28	1.73	942	<2	0.08	40	2801	32	0.03	<5	7	126	5	0.30	<10	<10	132	<10	83	10
44803	<0.2	2.73	<5	122	1.1	<5	3.47	1	30	234	<1	4.99	<1	0.15	27	3.09	1944	<2	0.04	61	2651	22	0.05	<5	11	188	9	0.32	<10	<10	133	<10	112	12
44804	<0.2	4.55	<5	137	1.0	<5	2.64	2	33	40	<1	5.81	1	1.36	<10	3.59	1878	<2	0.23	26	1107	87	0.05	<5	17	189	<5	0.28	<10	<10	238	<10	235	5
44805	<0.2	5.17	<5	225	<0.5	<5	1.68	<1	33	36	<1	5.49	<1	1.89	<10	3.76	609	<2	0.30	27	1083	3	<0.01	<5	20	167	<5	0.20	<10	<10	264	<10	54	3
44806	<0.2	4.49	<5	167	0.9	<5	2.12	1	18	17	<1	5.28	1	1.94	<10	2.99	551	<2	0.33	12	970	<2	0.01	<5	15	165	<5	0.24	<10	<10	231	<10	21	4
44807	<0.2	5.08	<5	203	0.9	<5	2.55	1	35	50	<1	5.86	1	1.85	<10	3.19	528	<2	0.44	34	888	5	0.01	<5	15	197	<5	0.28	<10	<10	254	<10	45	6
44808	<0.2	5.70	<5	96	0.8	<5	2.57	2	45	85	<1	6.99	<1	0.90	<10	5.58	2358	<2	0.17	54	800	373	0.08	<5	24	202	<5	0.24	<10	<10	277	<10	207	6
Duplicates:																																		
44801	<0.2	0.99	7	49	0.5	<5	3.29	1	62	475	12	4.15	<1	0.09	12	5.69	977	5	0.04	1130	1222	11	0.24	7	3	86	6	0.16	<10	<10	47	<10	29	13
Standards:																																		
Blank	<0.2	<0.01	<5	<10	<0.5	<5	<0.01	<1	<1	<1	<1	<0.01	<1	<0.01	<10	<0.01	<5	<2	<0.01	<1	<10	<2	<0.01	<5	<1	<1	<5	<0.01	<10	<10	<1	<10	3	<1
ICP-2	0.2	1.64	52	187	0.5	<5	4.04	3	85	184	1223	6.22	1	0.23	18	1.54	1737	5	0.02	98	1205	58	1.98	5	8	467	<5	0.02	<10	<10	120	<10	313	13

A .5 gm sample is digested with 5 ml 3:1 HCl/HNO3 at 95°C for 2 hours and diluted to 25ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2905RJ

Date : Sep-18-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

Multi-Element ICP-AES Analysis

Aqua Regia Digestion

Sample Number	Ag ppm	Al %	As ppm	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	Hg ppm	K %	La ppm	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	S %	Sb ppm	Sc ppm	Sr ppm	Th ppm	Ti %	Tl ppm	U ppm	V ppm	W ppm	Zn ppm	Zr ppm
44908	0.4	5.52	<5	381	<0.5	<5	0.78	<1	39	279	13	6.25	<1	1.50	<10	9.13	1972	<2	0.05	286	1216	80	0.05	<5	9	144	<5	0.16	<10	<10	115	<10	179	3
44909	0.5	2.46	5	360	<0.5	<5	1.14	1	67	502	18	5.17	<1	1.27	<10	10.22	1304	<2	0.08	942	1015	882	0.20	5	7	136	<5	0.15	<10	<10	77	<10	534	3
44910	1.1	5.18	<5	307	<0.5	<5	1.25	4	31	133	30	7.44	<1	1.05	20	5.43	4111	<2	0.11	117	1759	308	0.10	<5	10	136	<5	0.22	<10	12	134	13	943	4
44911	2.3	3.25	9	238	<0.5	<5	2.53	6	46	138	205	5.78	<1	0.92	20	2.47	1255	<2	0.24	98	1975	606	1.23	<5	9	234	<5	0.25	<10	<10	129	13	1313	6
44912	<0.2	1.83	<5	641	<0.5	<5	1.67	<1	30	124	27	4.28	<1	0.97	30	1.97	572	<2	0.11	37	2545	16	0.04	<5	4	125	6	0.30	<10	<10	112	<10	76	10
44913	1.3	2.49	<5	391	<0.5	<5	1.95	3	30	138	66	5.21	<1	0.74	33	2.43	2215	<2	0.08	36	2488	509	0.15	<5	7	138	7	0.24	<10	<10	115	<10	843	9
44914	118.1	3.55	20	22	<0.5	291	1.98	31	117	101	7785	10.35	<1	0.05	18	2.43	4477	<2	0.01	62	1604	3353	3.64	<5	7	65	<5	0.02	<10	19	75	31	6061	5
44915	10.9	3.62	<5	22	<0.5	39	1.95	30	34	107	626	7.85	<1	0.07	28	2.61	4413	6	0.01	35	1694	327	0.68	<5	6	79	6	0.01	<10	14	83	60	6091	5
44916	3.5	3.02	<5	55	<0.5	<5	2.24	4	21	104	228	5.95	<1	0.20	34	2.18	3768	2	0.02	23	2362	408	0.17	<5	6	157	10	0.10	<10	<10	90	12	1182	6
44917	1.6	2.56	<5	142	<0.5	<5	2.38	4	25	107	156	5.05	<1	0.42	33	2.11	2554	2	0.06	24	2586	461	0.23	<5	7	208	11	0.19	<10	<10	107	11	1017	8
44918	0.9	2.42	<5	117	<0.5	<5	3.13	<1	30	156	210	4.77	<1	0.74	28	2.39	1770	<2	0.08	34	2490	70	0.42	<5	8	203	8	0.25	<10	<10	111	<10	154	8
44919	35.0	4.63	<5	37	<0.5	61	2.57	2	31	110	2956	9.87	<1	0.21	34	3.08	5062	<2	0.02	44	2116	2306	0.69	<5	7	154	9	0.05	<10	18	98	<10	961	7
44920	3.5	5.21	<5	41	<0.5	8	1.41	9	31	70	145	10.49	<1	0.11	35	3.65	5348	3	0.01	13	2059	747	0.27	<5	8	64	10	0.09	<10	18	117	25	2281	6
44921	4.6	3.27	<5	78	<0.5	11	1.88	2	23	54	144	6.75	<1	0.33	23	2.09	3316	<2	0.04	6	1919	422	0.74	<5	7	585	<5	0.11	<10	<10	101	<10	640	4
44922	0.9	2.60	<5	70	<0.5	<5	3.04	<1	27	47	16	5.62	<1	0.46	17	2.30	2103	<2	0.08	27	2045	175	1.55	<5	8	399	<5	0.21	<10	<10	120	<10	390	5
44923	<0.2	2.04	<5	61	<0.5	<5	3.33	<1	25	165	14	4.14	<1	0.29	27	2.33	1377	<2	0.08	28	2320	30	0.16	<5	6	168	5	0.23	<10	<10	79	<10	123	6
44924	0.2	2.53	<5	210	<0.5	<5	2.79	1	30	198	17	4.25	<1	0.67	19	2.94	1283	<2	0.11	107	2241	256	0.19	5	5	226	<5	0.23	<10	<10	89	<10	270	5
44933	1.0	3.27	<5	148	<0.5	<5	2.31	8	29	188	45	6.39	<1	0.35	29	2.96	2793	<2	0.07	38	2286	43	0.22	<5	10	176	5	0.17	<10	<10	118	21	1786	5
44934	0.3	2.77	<5	238	<0.5	<5	2.49	1	28	215	21	5.47	<1	0.69	31	2.90	1931	<2	0.09	39	2417	18	0.09	<5	10	191	5	0.23	<10	<10	124	<10	416	5
44935	1.2	3.90	<5	237	<0.5	<5	2.53	<1	32	231	104	7.31	<1	0.56	34	3.71	2830	<2	0.05	44	2316	47	0.07	<5	14	215	6	0.17	<10	<10	141	<10	276	5
44936	0.9	3.56	<5	235	<0.5	<5	2.19	<1	29	101	55	6.92	<1	0.72	28	2.96	2494	<2	0.08	22	2181	30	0.20	<5	13	194	5	0.18	<10	<10	144	<10	398	5
44937	5.0	4.82	<5	41	<0.5	12	1.94	6	29	87	261	9.52	<1	0.11	28	4.39	3745	<2	0.02	32	1806	462	0.34	<5	10	87	5	0.04	<10	12	113	17	1516	4
44938	18.1	4.17	<5	33	<0.5	46	1.66	13	27	52	692	8.31	<1	0.08	28	3.50	3485	<2	0.02	27	1673	1828	0.38	<5	9	77	5	0.04	<10	10	104	32	3002	4
44939	1.3	4.29	<5	41	<0.5	11	1.27	<1	24	57	27	8.49	<1	0.10	35	3.42	3491	<2	0.02	14	1870	41	0.07	<5	10	61	6	0.05	<10	<10	108	<10	267	4
44940	0.2	2.09	<5	319	<0.5	<5	1.09	<1	25	134	18	3.62	<1	1.07	32	2.13	500	<2	0.15	47	2054	31	0.01	5	3	122	8	0.25	<10	<10	93	<10	141	6
44941	<0.2	3.04	<5	297	<0.5	<5	1.78	<1	27	160	30	4.04	<1	1.45	26	2.31	552	<2	0.33	39	2089	7	<0.01	6	3	297	<5	0.29	<10	<10	106	<10	75	6
44942	<0.2	3.18	<5	258	<0.5	<5	1.76	<1	28	153	21	4.04	<1	1.41	25	2.43	470	<2	0.35	40	2049	8	<0.01	6	3	312	<5	0.30	<10	<10	107	<10	86	6
44943	<0.2	3.03	<5	250	<0.5	<5	1.65	<1	28	162	18	4.02	<1	1.27	25	2.47	532	<2	0.29	40	2085	7	<0.01	6	3	267	<5	0.30	<10	<10	108	<10	110	6
44944	<0.2	3.39	<5	265	<0.5	<5	1.95	<1	28	195	13	4.46	<1	1.20	27	3.11	818	<2	0.27	43	2076	10	0.01	6	8	265	<5	0.25	<10	<10	122	<10	87	6
44945	<0.2	3.67	<5	251	<0.5	<5	4.00	<1	28	209	18	4.72	<1	1.23	25	3.52	1037	<2	0.26	44	1939	8	0.02	5	9	408	<5	0.23	<10	<10	131	<10	82	6

A .5 gm sample is digested with 5 ml 3:1 HCl/HNO3 at 95°C for 2 hours and diluted to 25ml.

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

Assayers Canada
8282 Sherbrooke St., Vancouver, B.C., V5X 4R6
Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2905RJ
Date : Sep-18-08

Multi-Element ICP-AES Analysis
Aqua Regia Digestion

Sample Number	Ag ppm	Al %	As ppm	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	Hg ppm	K %	La ppm	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	S %	Sb ppm	Sc ppm	Sr ppm	Th ppm	Ti %	Tl ppm	U ppm	V ppm	W ppm	Zn ppm	Zr ppm
44946	<0.2	3.73	<5	357	<0.5	<5	2.70	<1	30	200	18	4.36	<1	1.83	23	2.88	685	<2	0.40	42	2041	12	0.02	7	6	423	<5	0.32	<10	<10	125	<10	73	7
44947	<0.2	3.35	<5	293	<0.5	<5	2.62	<1	29	178	14	4.30	<1	1.52	21	2.89	711	<2	0.31	41	1964	13	0.02	6	5	351	<5	0.30	<10	<10	119	<10	74	7
44948	<0.2	3.62	<5	350	<0.5	<5	2.92	<1	30	182	33	4.38	<1	1.79	23	3.02	885	<2	0.35	42	2018	23	0.02	6	6	389	<5	0.31	<10	<10	123	<10	80	7
44949	<0.2	3.72	<5	359	<0.5	<5	2.60	<1	30	172	17	4.23	<1	1.82	22	2.87	659	<2	0.40	41	2065	14	0.01	7	5	414	<5	0.33	<10	<10	122	<10	75	7
44950	<0.2	3.87	<5	336	<0.5	<5	3.14	<1	31	197	25	4.55	<1	1.76	24	3.16	746	<2	0.38	44	2043	8	0.02	7	8	428	<5	0.31	<10	<10	133	<10	66	7
45003	<0.2	2.07	<5	313	<0.5	<5	2.25	<1	20	101	15	4.12	<1	0.44	67	2.81	1887	<2	0.06	42	2178	17	0.07	<5	6	112	16	0.16	<10	<10	86	<10	94	24
45004	<0.2	1.80	<5	384	<0.5	<5	2.51	<1	21	92	28	3.87	<1	0.53	56	2.59	1303	<2	0.07	39	2006	18	0.11	<5	6	126	14	0.21	<10	<10	85	<10	66	28
45005	<0.2	1.28	<5	506	<0.5	<5	1.92	<1	21	92	33	3.65	<1	0.78	51	1.79	650	2	0.10	26	1965	22	0.03	5	6	103	14	0.29	<10	<10	88	<10	40	39
45006	<0.2	1.29	<5	500	<0.5	<5	1.75	<1	21	87	21	3.58	<1	0.79	50	1.81	617	2	0.11	25	1947	34	0.04	<5	5	101	14	0.28	<10	<10	85	<10	53	36
45007	<0.2	1.17	<5	472	<0.5	<5	1.77	<1	20	79	19	3.45	<1	0.78	47	1.69	585	2	0.09	24	1871	16	0.03	<5	5	92	13	0.27	<10	<10	81	<10	33	34
45008	<0.2	1.14	<5	413	<0.5	<5	1.54	<1	18	77	21	3.13	<1	0.68	44	1.63	543	<2	0.10	21	1718	18	0.02	<5	4	85	13	0.24	<10	<10	72	<10	36	32
45009	<0.2	1.32	<5	448	<0.5	<5	1.48	<1	20	75	21	3.32	<1	0.88	40	1.84	546	<2	0.09	24	1681	23	0.02	<5	5	79	9	0.24	<10	<10	89	<10	47	28
45010	<0.2	1.71	<5	463	<0.5	<5	1.31	<1	22	60	23	3.90	<1	1.21	33	2.06	637	<2	0.13	20	1484	13	0.04	<5	7	73	8	0.25	<10	<10	121	<10	46	28
45011	<0.2	1.28	<5	464	<0.5	<5	1.64	<1	20	77	17	3.31	<1	0.76	47	1.72	548	2	0.09	23	1836	16	0.04	<5	5	91	13	0.26	<10	<10	80	<10	36	33
45012	<0.2	2.01	<5	314	<0.5	<5	2.19	<1	19	85	23	3.37	<1	0.55	44	3.47	1137	2	0.06	45	1732	19	0.07	<5	5	102	9	0.21	<10	<10	74	<10	65	21
45067	<0.2	2.91	<5	553	<0.5	<5	2.41	<1	27	117	19	4.19	<1	1.08	36	2.62	409	<2	0.10	57	2395	10	0.01	7	3	368	5	0.31	<10	<10	102	<10	42	7
Duplicates:																																		
44923	<0.2	1.99	<5	62	<0.5	<5	3.33	<1	26	164	13	4.20	<1	0.29	27	2.28	1384	<2	0.07	29	2321	30	0.16	5	7	166	5	0.23	<10	<10	80	<10	128	6
44942	<0.2	3.24	<5	269	<0.5	<5	1.82	<1	29	161	22	4.21	<1	1.44	26	2.48	489	<2	0.35	42	2128	8	<0.01	6	3	324	5	0.31	<10	<10	112	<10	88	7
44945	<0.2	3.12	<5	210	<0.5	<5	3.29	<1	24	177	15	4.03	<1	1.04	21	3.02	881	<2	0.22	36	1667	7	0.02	5	8	337	<5	0.19	<10	<10	110	<10	68	5
45004	<0.2	1.63	<5	356	<0.5	<5	2.23	<1	19	85	26	3.47	<1	0.48	50	2.36	1190	<2	0.06	35	1867	15	0.10	<5	6	113	12	0.19	<10	<10	78	<10	61	26
Standards:																																		
Blank	<0.2	<0.01	<5	<10	<0.5	<5	<0.01	<1	<1	<1	1	<0.01	<1	<0.01	<10	<0.01	<5	<2	0.01	<1	<10	<2	<0.01	<5	<1	<1	<5	<0.01	<10	<10	<1	<10	2	<1
ICP-2	0.9	1.60	45	160	<0.5	<5	3.72	1	77	164	1074	5.78	1	0.24	15	1.53	1508	4	0.03	87	1045	65	1.88	<5	7	434	<5	0.01	<10	<10	104	<10	289	8

A .5 gm sample is digested with 5 ml 3:1 HCl/HNO3 at 95°C for 2 hours and diluted to 25ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2906RJ

Date : Nov-28-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

Multi-Element ICP-AES Analysis

Aqua Regia Digestion

Sample Number	Ag ppm	Al %	As ppm	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	Hg ppm	K %	La ppm	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	S %	Sb ppm	Sc ppm	Sr ppm	Th ppm	Ti %	Tl ppm	U ppm	V ppm	W ppm	Zn ppm	Zr ppm
45184	<0.2	2.91	5	268	1.6	<5	2.23	2	30	159	13	6.42	<1	0.36	42	3.92	2486	2	0.05	116	2415	17	0.87	<5	6	183	10	0.20	<10	<10	96	<10	163	34
45185	<0.2	1.67	<5	425	1.9	<5	2.24	1	20	122	18	4.25	<1	0.57	51	1.81	1214	5	0.08	32	2372	17	0.03	<5	4	156	12	0.28	<10	<10	94	<10	102	37
45186	<0.2	1.21	<5	509	1.7	<5	2.02	1	19	91	23	3.68	<1	0.71	47	1.57	630	4	0.07	30	2429	29	0.02	<5	3	143	12	0.32	<10	<10	91	<10	42	38
45187	<0.2	1.25	<5	322	1.4	<5	1.77	1	17	84	30	3.68	<1	0.59	44	1.30	491	4	0.09	25	2337	14	0.02	<5	4	180	16	0.27	<10	10	94	<10	51	22
45188	<0.2	1.27	<5	320	1.2	<5	1.12	1	15	87	22	3.22	<1	0.67	38	1.02	296	2	0.13	21	2168	10	0.01	<5	3	193	17	0.27	<10	11	89	<10	57	13
45189	<0.2	1.22	<5	305	1.3	<5	1.46	1	15	72	22	3.29	<1	0.57	37	1.07	372	2	0.09	22	2208	9	0.01	<5	3	206	18	0.24	<10	<10	93	<10	55	11
45190	<0.2	1.16	<5	315	1.2	<5	1.15	1	14	62	20	2.99	<1	0.63	37	0.88	273	2	0.07	19	2254	8	0.01	<5	2	377	17	0.25	<10	<10	87	<10	56	10
45191	<0.2	1.25	<5	310	1.3	<5	1.28	1	15	71	20	3.14	<1	0.60	38	1.00	338	2	0.08	20	2222	15	0.02	<5	3	341	18	0.26	<10	<10	91	<10	51	12
45192	<0.2	1.12	<5	274	1.2	<5	1.27	1	14	70	18	3.08	<1	0.53	40	0.99	377	3	0.07	20	2229	18	0.01	<5	2	201	18	0.24	<10	<10	89	<10	50	14
45193	<0.2	1.14	<5	451	1.4	<5	2.05	1	19	74	23	3.51	<1	0.56	46	1.52	580	3	0.05	28	2392	32	0.01	<5	3	170	9	0.29	<10	<10	85	<10	53	29
Duplicates:																																		
45184	<0.2	2.83	<5	267	1.6	<5	2.17	2	29	156	11	6.29	<1	0.35	42	3.83	2439	2	0.04	113	2372	13	0.86	<5	6	178	9	0.20	<10	<10	95	<10	156	36
45193	<0.2	1.11	<5	422	1.4	<5	2.05	1	18	76	23	3.49	<1	0.53	46	1.48	577	3	0.05	28	2372	28	0.01	<5	3	172	10	0.28	<10	<10	84	<10	51	30
Standards:																																		
Blank	<0.2	<0.01	<5	<10	<0.5	<5	<0.01	<1	<1	<1	<1	<0.01	<1	<0.01	<10	<0.01	<5	<2	0.01	<1	<10	<2	<0.01	<5	<1	<1	<5	<0.01	<10	16	<1	<10	<1	<1
ICP-2	0.4	1.56	51	182	0.5	<5	3.88	3	81	177	1156	5.99	1	0.22	17	1.48	1663	5	0.02	95	1117	61	1.92	5	7	447	<5	0.02	<10	<10	115	<10	290	12

A .5 gm sample is digested with 5 ml 3:1 HCl/HNO3 at 95°C for 2 hours and diluted to 25ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2995RJ

Date : Dec-05-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

Multi-Element ICP-AES Analysis

Aqua Regia Digestion

Sample Number	Ag ppm	Al %	As ppm	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	Hg ppm	K %	La ppm	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	S %	Sb ppm	Sc ppm	Sr ppm	Th ppm	Ti %	Tl ppm	U ppm	V ppm	W ppm	Zn ppm	Zr ppm
45283	<0.2	4.07	<5	119	0.9	<5	0.69	2	32	30	<1	6.12	<1	0.41	<10	4.97	2658	<2	0.11	53	785	52	0.01	<5	20	22	<5	0.20	<10	<10	249	<10	162	5
45284	<0.2	2.99	<5	699	2.2	<5	1.14	1	41	176	49	4.99	<1	1.30	17	3.89	1322	<2	0.08	121	2725	14	0.01	<5	5	86	6	0.44	<10	<10	127	<10	80	21
45285	<0.2	3.32	<5	114	1.0	<5	1.57	2	35	42	<1	6.02	<1	0.61	<10	3.31	2090	<2	0.16	28	771	34	0.01	<5	18	60	<5	0.25	<10	<10	259	<10	116	7
45286	<0.2	3.16	<5	178	1.1	<5	1.64	2	37	35	8	5.82	<1	0.93	<10	2.87	951	<2	0.20	22	734	12	0.01	<5	15	118	<5	0.27	<10	<10	253	<10	62	8
45287	<0.2	3.21	<5	214	1.2	<5	1.56	2	35	30	2	6.13	<1	1.35	<10	2.64	1134	<2	0.18	12	730	<2	0.01	<5	12	118	<5	0.30	<10	<10	272	<10	58	8
45288	<0.2	3.00	<5	172	1.0	<5	0.93	2	27	22	9	5.49	<1	1.26	<10	2.51	1280	<2	0.14	13	775	7	0.03	<5	13	81	<5	0.26	<10	<10	231	<10	76	6
45289	<0.2	4.32	<5	117	1.0	<5	0.48	2	32	18	9	6.21	<1	0.88	<10	4.51	3321	<2	0.05	14	836	40	0.03	<5	19	63	<5	0.23	<10	<10	254	<10	231	5
45290	<0.2	4.43	<5	250	0.7	<5	0.97	1	31	63	46	4.63	<1	1.53	<10	4.69	623	<2	0.14	118	658	3	0.02	<5	13	258	<5	0.17	<10	<10	191	<10	80	4
Duplicates:																																		
45283	<0.2	4.04	<5	123	0.9	<5	0.69	2	31	34	<1	6.06	<1	0.41	<10	4.88	2637	<2	0.11	48	771	50	0.01	<5	20	22	<5	0.19	<10	<10	250	<10	163	5
Standards:																																		
Blank	<0.2	<0.01	<5	<10	<0.5	<5	<0.01	<1	<1	<1	<1	<0.01	<1	<0.01	<10	<0.01	<5	<2	<0.01	<1	<10	<2	<0.01	<5	<1	<1	<5	<0.01	<10	<10	<1	<10	<1	<1
ICP-2	0.4	1.51	49	184	0.5	<5	3.68	3	79	172	1096	5.65	1	0.22	16	1.41	1569	5	0.02	93	1106	55	1.83	5	7	430	<5	0.02	<10	<10	113	<10	291	12

A .5 gm sample is digested with 5 ml 3:1 HCl/HNO3 at 95°C for 2 hours and diluted to 25ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V3085RJ

Date : Dec-01-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

Multi-Element ICP-AES Analysis

Aqua Regia Digestion

Sample Number	Ag ppm	Al %	As ppm	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	Hg ppm	K %	La ppm	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	S %	Sb ppm	Sc ppm	Sr ppm	Th ppm	Ti %	Tl ppm	U ppm	V ppm	W ppm	Zn ppm	Zr ppm
45332	<0.2	1.95	<5	409	1.7	<5	3.80	1	21	148	16	3.35	1	0.58	37	4.56	1413	<2	0.05	129	1560	57	0.01	<5	4	122	11	0.25	<10	<10	74	<10	107	43
45333	<0.2	1.29	<5	469	2.0	<5	1.69	1	19	92	17	3.46	<1	0.70	49	1.65	677	<2	0.09	29	2259	40	0.01	<5	4	102	13	0.30	<10	<10	87	<10	47	46
45334	<0.2	1.22	<5	511	2.1	<5	1.82	1	19	100	19	3.56	<1	0.72	49	1.59	594	<2	0.10	29	2262	9	0.01	<5	4	110	13	0.32	<10	<10	91	<10	25	47
45335	<0.2	1.27	<5	460	2.1	<5	1.66	1	24	134	15	3.50	<1	0.63	45	2.71	580	<2	0.08	158	2063	10	0.01	<5	4	105	14	0.29	<10	<10	81	<10	26	48
45336	<0.2	1.13	<5	488	2.1	<5	1.59	1	19	95	20	3.37	<1	0.65	49	1.44	560	<2	0.09	30	2238	16	<0.01	<5	3	102	17	0.30	<10	<10	86	<10	28	42
45337	<0.2	1.14	<5	482	2.1	<5	1.67	1	19	97	19	3.49	<1	0.64	49	1.45	545	<2	0.08	28	2275	15	<0.01	<5	3	108	18	0.31	<10	<10	87	<10	24	47
45338	<0.2	1.19	<5	474	2.2	<5	1.82	1	19	91	24	3.41	<1	0.64	47	1.48	562	<2	0.09	27	2172	16	<0.01	<5	4	125	16	0.30	<10	<10	85	<10	29	51
45339	<0.2	1.21	<5	475	2.0	<5	1.67	1	18	94	12	3.36	1	0.72	48	1.54	556	<2	0.10	27	2144	9	0.01	<5	4	108	15	0.30	<10	<10	83	<10	35	51
45396	0.2	1.78	<5	253	1.4	<5	1.56	4	26	170	31	3.77	1	0.37	26	3.08	1346	<2	0.05	152	2404	412	0.09	<5	5	95	8	0.26	<10	<10	96	<10	750	9
Duplicates:																																		
45332	<0.2	2.05	<5	436	1.7	<5	3.88	1	21	141	16	3.45	<1	0.63	36	4.76	1437	<2	0.05	129	1576	58	0.01	<5	4	126	12	0.25	<10	<10	76	<10	110	36
Standards:																																		
Blank	<0.2	<0.01	<5	<10	<0.5	<5	<0.01	<1	<1	<1	<1	<0.01	1	<0.01	<10	<0.01	<5	<2	<0.01	<1	<10	<2	<0.01	<5	<1	<1	<5	<0.01	<10	<10	<1	<10	<1	<1
ICP-2	0.4	1.50	50	192	0.5	<5	3.75	3	79	171	1114	5.76	1	0.21	16	1.43	1605	5	0.02	94	1122	56	1.85	<5	7	432	<5	0.02	<10	<10	112	<10	281	12

A .5 gm sample is digested with 5 ml 3:1 HCl/HNO3 at 95°C for 2 hours and diluted to 25ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V3176RJ

Date : Dec-02-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type: Drill Core

Multi-Element ICP-AES Analysis

Aqua Regia Digestion

Sample Number	Ag ppm	Al %	As ppm	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	Hg ppm	K %	La ppm	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	S %	Sb ppm	Sc ppm	Sr ppm	Th ppm	Ti %	Tl ppm	U ppm	V ppm	W ppm	Zn ppm	Zr ppm
45588	<0.2	1.75	<5	407	<0.5	<5	3.66	<1	21	122	26	3.80	<1	0.53	64	2.34	963	<2	0.08	36	2429	67	<0.01	<5	6	185	13	0.20	<10	<10	95	<10	75	32
45589	<0.2	1.27	<5	605	<0.5	<5	1.90	<1	25	117	21	3.93	<1	0.82	63	1.66	660	<2	0.11	41	2595	31	0.01	<5	4	109	20	0.32	<10	<10	108	<10	44	23
45590	<0.2	1.29	<5	606	<0.5	<5	1.86	<1	24	118	18	3.84	1	0.84	59	1.57	623	<2	0.11	34	2542	22	0.02	<5	4	114	19	0.33	<10	<10	105	<10	37	24
Duplicates:																																		
45588	<0.2	1.71	<5	389	<0.5	<5	3.55	<1	21	111	25	3.68	<1	0.51	61	2.28	922	<2	0.07	34	2308	64	<0.01	<5	6	175	12	0.19	<10	<10	91	<10	71	31
Standards:																																		
Blank	<0.2	<0.01	<5	<10	<0.5	<5	<0.01	<1	1	<1	<1	<0.01	<1	<0.01	<10	<0.01	<5	<2	<0.01	<1	<10	<2	<0.01	<5	<1	<1	<5	<0.01	<10	<10	<1	<10	<1	<1
ICP-2	1.1	1.56	50	240	<0.5	<5	3.97	1	87	191	1167	5.94	1	0.23	17	1.53	1720	5	0.02	94	1147	68	2.06	<5	8	473	<5	0.02	<10	<10	123	<10	325	9

A .5 gm sample is digested with 5 ml 3:1 HCl/HNO3 at 95°C for 2 hours and diluted to 25ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V3313RJ

Date : Dec-16-08

WHY Resources

Attention: Mitchell Marasco

Project: Record Ridge South

Sample type: Rock

Multi-Element ICP-AES Analysis

Aqua Regia Digestion

Sample Number	Ag ppm	Al %	As ppm	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	Hg ppm	K %	La ppm	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	S %	Sb ppm	Sc ppm	Sr ppm	Th ppm	Ti %	Tl ppm	U ppm	V ppm	W ppm	Zn ppm	Zr ppm
45816	<0.2	1.98	14	193	<0.5	<5	0.51	<1	24	144	28	3.87	<1	0.25	45	4.39	950	<2	0.06	164	1921	30	0.01	<5	8	33	20	0.19	<10	<10	103	<10	66	20
45817	<0.2	1.30	<5	476	<0.5	<5	0.67	<1	24	110	18	4.12	<1	0.53	59	2.04	728	<2	0.10	66	2738	13	0.01	<5	6	61	17	0.38	<10	<10	94	<10	38	37
45818	<0.2	1.40	<5	487	<0.5	<5	0.69	<1	23	99	18	4.05	<1	0.53	60	1.87	723	<2	0.10	42	2696	16	0.01	<5	6	60	17	0.37	<10	<10	91	<10	39	36
45819	<0.2	1.38	<5	520	<0.5	<5	0.64	<1	24	105	16	3.97	<1	0.55	59	1.83	713	<2	0.10	37	2634	16	0.01	<5	6	62	16	0.39	<10	<10	95	<10	41	41
45820	<0.2	1.71	<5	430	<0.5	<5	0.67	<1	23	114	37	4.53	<1	0.49	64	2.16	1441	<2	0.09	50	2928	146	0.01	<5	8	59	18	0.34	<10	<10	99	<10	154	34
45821	2.1	2.96	<5	86	<0.5	6	0.63	11	21	122	40	6.20	1	0.15	74	2.58	4809	<2	0.01	46	3480	3510	<0.01	<5	7	32	21	0.02	<10	<10	230	38	2382	15
45822	0.5	2.76	<5	97	<0.5	5	0.63	11	22	115	2	5.63	<1	0.14	65	2.44	4739	<2	0.01	48	3246	807	<0.01	<5	7	31	18	0.03	<10	<10	96	20	1178	12
45823	<0.2	1.58	<5	462	<0.5	<5	0.69	3	22	105	18	4.30	<1	0.58	63	1.98	1544	<2	0.09	44	2940	219	0.01	<5	6	55	18	0.31	<10	<10	98	<10	282	38
45824	<0.2	1.49	<5	621	<0.5	<5	0.72	<1	24	108	22	4.30	<1	0.69	68	1.99	680	<2	0.11	35	2939	26	0.01	<5	6	63	21	0.40	<10	<10	108	<10	49	40
45825	<0.2	1.30	<5	558	<0.5	<5	0.77	<1	22	101	18	3.96	<1	0.67	62	1.76	649	<2	0.10	32	2823	28	0.01	<5	5	64	18	0.37	<10	<10	95	<10	43	31
45826	<0.2	1.46	<5	598	<0.5	<5	0.78	<1	24	113	20	4.36	<1	0.69	65	1.93	690	<2	0.12	35	3011	23	0.01	<5	5	67	19	0.40	<10	<10	105	<10	41	36
45827	<0.2	1.26	<5	559	<0.5	<5	0.72	<1	21	94	19	3.85	<1	0.68	58	1.71	578	<2	0.11	32	2595	19	0.01	<5	4	62	17	0.33	<10	<10	93	<10	35	32
45828	<0.2	1.46	<5	596	<0.5	<5	0.73	<1	22	99	20	4.06	<1	0.71	65	2.02	604	<2	0.12	32	2748	16	0.01	<5	5	66	20	0.35	<10	<10	98	<10	36	31
45829	<0.2	1.66	<5	560	<0.5	<5	1.14	<1	26	128	18	4.07	<1	0.71	58	2.89	675	<2	0.11	111	2684	11	<0.01	<5	6	85	17	0.36	<10	<10	93	<10	40	42
Duplicates:																																		
45816	<0.2	2.20	15	213	<0.5	<5	0.56	<1	26	160	31	4.29	<1	0.27	50	4.88	1048	<2	0.06	181	2092	35	0.01	<5	9	36	22	0.23	<10	<10	115	<10	74	23
45825	<0.2	1.31	<5	565	<0.5	<5	0.77	<1	22	102	18	4.09	<1	0.67	61	1.78	656	<2	0.11	32	2812	26	0.01	<5	5	65	19	0.37	<10	<10	96	<10	42	33
Standards:																																		
Blank	<0.2	<0.01	<5	<10	<0.5	<5	<0.01	<1	<1	<1	1	<0.01	<1	<0.01	<10	<0.01	<5	<2	0.01	<1	<10	<2	<0.01	<5	<1	<1	<5	<0.01	<10	<10	<1	<10	<1	<1
ICP-2	0.6	1.60	63	163	<0.5	<5	4.04	2	83	190	1122	6.35	1	0.25	16	1.58	1722	7	0.02	100	1320	66	1.98	<5	8	451	<5	0.02	<10	<10	118	<10	312	11

A .5 gm sample is digested with 5 ml 3:1 HCl/HNO3 at 95°C for 2 hours and diluted to 25ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V3324RJ

Date : Dec-05-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type: Core

Multi-Element ICP-AES Analysis

Aqua Regia Digestion

Sample Number	Ag ppm	Al %	As ppm	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	Hg ppm	K %	La ppm	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	S %	Sb ppm	Sc ppm	Sr ppm	Th ppm	Ti %	Tl ppm	U ppm	V ppm	W ppm	Zn ppm	Zr ppm			
45912	<0.2	1.41	12	421	<0.5	<5	0.74	<1	24	158	24	3.93	<1	0.61	50	2.48	723	<2	<0.01	110	2394	42	0.02	13	5	53	12	0.31	<10	61	143	<10	53	43			
45913	<0.2	1.47	12	532	<0.5	<5	1.42	<1	22	163	19	4.02	<1	0.75	48	2.03	792	<2	<0.01	39	2529	37	0.02	13	5	78	11	0.34	<10	69	158	<10	50	46			
45914	<0.2	2.14	16	390	<0.5	<5	2.13	<1	34	312	15	4.63	<1	0.54	35	4.59	2065	<2	<0.01	256	2331	107	0.02	15	6	365	6	0.23	<10	58	161	<10	131	44			
Duplicates:																																					
45912	<0.2	1.36	11	416	<0.5	<5	0.76	<1	23	194	24	3.93	<1	0.60	41	2.51	716	<2	<0.01	119	2445	41	0.02	13	5	52	8	0.30	<10	74	157	<10	54	45			
Standards:																																					
Blank	<0.2	<0.01	<5	<10	<0.5	<5	<0.01	<1	1	1	<1	0.01	<1	<0.01	<10	<0.01	<5	<2	<0.01	<1	<10	3	<0.01	<5	<1	<1	<5	<0.01	<10	<10	<1	<10	<1	<1			
ICP-2	<0.2	1.66	58	178	<0.5	<5	4.31	1	86	178	1148	6.24	<1	0.27	14	1.63	1663	6	<0.01	97	1207	77	1.88	14	8	452	<5	0.02	<10	<10	205	<10	302	13			

A .5 gm sample is digested with 5 ml 3:1 HCl/HNO3 at 95°C for 2 hours and diluted to 25ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V3723RJ

Date : Nov-06-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type: Drill Core

Multi-Element ICP-AES Analysis

Aqua Regia Digestion

Sample Number	Ag ppm	Al %	As ppm	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	Hg ppm	K %	La ppm	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	S %	Sb ppm	Sc ppm	Sr ppm	Th ppm	Ti %	Tl ppm	U ppm	V ppm	W ppm	Zn ppm	Zr ppm
46691	0.3	1.47	19	348	<0.5	<5	0.87	1	18	99	11	3.51	<1	0.65	34	1.50	520	<2	0.10	38	2402	152	0.02	<5	3	57	11	0.24	<10	<10	90	<10	256	11
46692	<0.2	1.51	18	192	<0.5	<5	1.21	<1	21	128	18	3.70	<1	0.63	36	1.87	713	<2	0.09	77	2659	64	<0.01	<5	3	79	9	0.25	<10	<10	90	<10	173	11
46693	<0.2	1.39	18	213	<0.5	<5	0.96	<1	28	160	13	3.83	<1	0.64	31	3.11	613	<2	0.08	211	2525	54	<0.01	<5	3	64	8	0.25	<10	<10	86	<10	161	10
46694	<0.2	3.03	13	118	<0.5	<5	0.65	<1	38	453	9	4.57	<1	0.24	15	6.67	648	<2	0.03	336	1902	65	<0.01	12	5	28	<5	0.14	<10	<10	123	<10	102	5
46695	<0.2	3.65	18	97	<0.5	<5	0.72	<1	35	271	12	5.31	<1	0.25	10	6.20	956	<2	0.04	256	1724	62	<0.01	9	14	45	<5	0.19	<10	<10	165	<10	177	5
46696	0.2	3.09	15	126	<0.5	<5	1.27	<1	34	79	17	6.30	<1	0.62	<10	3.72	698	<2	0.07	144	1132	60	<0.01	6	15	86	<5	0.27	<10	<10	221	<10	70	5
46697	<0.2	3.22	12	134	<0.5	<5	1.18	<1	32	53	20	5.78	<1	0.69	<10	3.85	545	<2	0.10	118	1244	36	<0.01	6	16	74	<5	0.23	<10	<10	216	<10	50	4
46698	<0.2	3.39	11	203	<0.5	<5	1.05	<1	32	25	12	5.97	<1	1.20	<10	3.67	423	<2	0.18	62	1273	34	<0.01	5	20	74	<5	0.24	<10	<10	263	<10	51	4
46699	<0.2	2.41	14	141	<0.5	<5	1.56	1	31	122	23	4.86	<1	0.71	<10	2.20	711	<2	0.14	148	1088	151	<0.01	6	10	77	<5	0.23	<10	<10	161	<10	85	4
46700	<0.2	3.43	12	192	<0.5	<5	1.63	<1	30	60	9	4.52	<1	1.15	<10	2.74	485	<2	0.25	141	1027	55	<0.01	5	13	152	<5	0.23	<10	<10	193	<10	51	3
Duplicates:																																		
46691	0.2	1.46	19	351	<0.5	<5	0.90	1	18	102	11	3.56	<1	0.65	34	1.53	527	<2	0.10	39	2407	155	0.02	<5	3	56	11	0.24	<10	<10	91	<10	262	11
46700	<0.2	3.39	13	189	<0.5	<5	1.58	<1	30	60	9	4.41	<1	1.14	<10	2.69	474	<2	0.25	138	1028	55	<0.01	6	13	150	<5	0.22	<10	<10	192	<10	50	3
Standards:																																		
Blank	<0.2	<0.01	<5	<10	<0.5	<5	<0.01	<1	<1	<1	<1	<0.01	<1	<0.01	<10	<0.01	<5	<2	<0.01	<1	<10	<2	<0.01	<5	<1	<1	<5	<0.01	<10	<10	<1	<10	<1	<1
ICP-2	0.6	1.54	69	210	0.9	<5	4.29	1	91	200	1070	6.17	<1	0.23	17	1.63	1676	6	0.02	95	1318	75	2.25	12	7	437	<5	0.02	<10	<10	123	<10	309	11

A .5 gm sample is digested with 5 ml 3:1 HCl/HNO3 at 95°C for 2 hours and diluted to 25ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V3790RJ

Date : Nov-13-08

WHY Resources

Attention: Frank Maraso

Project: Record Ridge South

Sample type: drill core

Multi-Element ICP-AES Analysis

Aqua Regia Digestion

Sample Number	Ag ppm	Al %	As ppm	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	Hg ppm	K %	La ppm	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	S %	Sb ppm	Sc ppm	Sr ppm	Th ppm	Ti %	Tl ppm	U ppm	V ppm	W ppm	Zn ppm	Zr ppm
46701	0.9	2.17	14	148	<0.5	<5	2.56	2	27	179	50	3.62	2	0.37	<10	2.26	1194	<2	0.06	327	937	74	0.10	5	5	154	<5	0.13	<10	<10	60	<10	206	6
46702	<0.2	3.41	5	180	<0.5	<5	1.63	1	24	57	6	4.92	2	1.16	<10	2.10	391	<2	0.28	73	1044	31	0.02	<5	11	132	<5	0.20	<10	<10	190	<10	38	5
46703	0.2	4.34	10	134	<0.5	<5	2.00	1	27	34	10	5.22	2	1.71	<10	2.61	736	<2	0.26	77	1039	38	0.01	<5	13	122	<5	0.18	<10	11	185	<10	48	5
46704	0.5	3.85	25	93	<0.5	<5	3.91	2	28	27	124	6.23	2	0.93	<10	2.05	1166	<2	0.25	35	844	29	<0.01	<5	8	153	<5	0.13	<10	15	130	<10	33	6
46705	<0.2	5.11	5	130	<0.5	<5	2.07	1	27	21	7	5.58	2	2.05	<10	2.40	374	<2	0.44	33	1100	35	<0.01	<5	18	112	<5	0.25	<10	<10	246	<10	27	5
46706	<0.2	3.77	25	101	<0.5	<5	4.12	2	24	130	7	6.84	1	1.66	<10	2.35	651	<2	0.22	103	836	26	<0.01	<5	14	101	<5	0.14	<10	14	178	<10	20	5
46707	<0.2	4.18	8	143	<0.5	<5	2.18	1	23	78	6	3.79	1	1.62	<10	2.06	413	<2	0.31	80	895	30	<0.01	<5	13	163	<5	0.17	<10	<10	160	<10	35	4
46708	0.3	3.06	26	131	<0.5	<5	2.90	1	21	79	9	4.52	1	1.14	<10	1.91	501	<2	0.19	106	692	20	<0.01	<5	9	99	<5	0.11	<10	10	110	<10	22	4
46709	<0.2	3.79	6	226	<0.5	<5	1.23	1	27	45	6	4.67	1	1.88	<10	2.57	352	<2	0.21	54	951	26	<0.01	<5	12	115	<5	0.13	<10	<10	160	<10	29	4
46710	<0.2	2.78	<5	90	<0.5	<5	1.00	1	21	44	7	3.37	1	1.16	<10	1.89	225	<2	0.19	35	772	20	<0.01	<5	9	67	<5	0.14	<10	<10	138	<10	19	3
46711	<0.2	3.30	<5	115	<0.5	<5	1.03	1	22	48	4	4.18	1	1.22	<10	2.45	217	<2	0.25	36	966	24	<0.01	<5	12	87	<5	0.17	<10	<10	175	<10	14	3
46712	0.5	3.25	<5	131	<0.5	<5	1.02	1	24	49	49	4.29	1	1.27	<10	2.63	242	<2	0.21	27	1018	26	<0.01	<5	13	82	<5	0.24	<10	<10	173	<10	17	4
46713	<0.2	3.93	6	102	<0.5	<5	1.50	1	28	79	18	4.55	<1	1.52	<10	3.84	377	<2	0.19	156	876	26	<0.01	<5	13	126	<5	0.16	<10	<10	155	<10	15	4
46714	<0.2	3.65	9	151	<0.5	<5	1.77	1	26	78	7	4.35	1	1.80	<10	2.87	381	<2	0.26	156	963	26	<0.01	<5	10	95	<5	0.19	<10	<10	141	<10	16	4
46715	<0.2	4.28	<5	154	<0.5	<5	1.38	1	26	44	3	4.87	1	2.28	<10	2.93	299	<2	0.35	29	1078	32	<0.01	<5	14	134	<5	0.25	<10	<10	181	<10	24	4
46716	0.8	4.64	<5	159	<0.5	<5	1.35	1	26	44	8	4.12	1	2.60	<10	3.17	290	<2	0.30	40	1087	32	<0.01	<5	14	163	<5	0.20	<10	<10	153	<10	34	4
46717	0.7	1.37	8	31	<0.5	<5	1.62	1	36	345	12	4.61	<1	0.27	<10	2.04	556	<2	0.05	676	499	14	<0.01	6	3	32	<5	0.07	<10	<10	50	<10	18	6
46718	<0.2	3.16	<5	117	<0.5	<5	1.15	1	21	39	3	3.42	1	1.31	<10	2.38	186	<2	0.26	59	962	24	<0.01	<5	8	143	<5	0.19	<10	<10	131	<10	12	3
46719	0.3	3.25	<5	103	<0.5	<5	1.48	1	27	87	5	2.64	<1	1.18	<10	3.40	285	<2	0.22	223	803	28	<0.01	<5	6	122	<5	0.12	<10	<10	89	<10	14	3
46720	1.6	2.31	8	359	<0.5	<5	0.98	1	52	262	51	4.05	<1	1.31	<10	4.02	395	<2	0.07	680	1575	29	0.02	7	4	64	<5	0.17	<10	<10	79	<10	24	12
46721	29.8	2.51	5	45	<0.5	<5	1.63	1	17	31	127	2.98	<1	1.34	<10	1.66	288	<2	0.14	34	1142	118	0.06	<5	8	123	<5	0.15	<10	<10	137	<10	28	3
46722	4.3	3.62	<5	148	<0.5	<5	1.16	1	26	37	47	4.08	1	2.13	<10	2.75	313	<2	0.22	65	1111	207	0.01	<5	10	136	<5	0.15	<10	<10	156	<10	28	4
46723	1.6	2.52	12	169	<0.5	<5	3.11	1	20	34	32	3.88	1	0.82	<10	2.51	609	<2	0.08	58	857	24	0.02	<5	5	148	<5	0.12	<10	<10	99	<10	26	4
46724	1.7	1.79	5	123	<0.5	<5	1.13	1	20	35	18	3.32	1	0.88	<10	1.80	259	<2	0.11	28	1062	20	0.01	<5	7	70	<5	0.16	<10	<10	130	<10	24	3
46725	<0.2	1.78	6	110	<0.5	<5	2.53	1	25	16	9	2.93	<1	0.83	<10	2.18	530	<2	0.08	72	989	17	0.01	<5	7	121	<5	0.17	<10	<10	127	<10	35	2
46726	<0.2	2.16	<5	125	<0.5	<5	2.23	1	28	115	4	3.41	<1	1.40	<10	3.13	576	<2	0.08	272	739	78	0.05	<5	6	93	<5	0.14	<10	<10	111	<10	57	2
46727	<0.2	1.14	5	57	<0.5	<5	2.37	1	20	83	5	2.97	<1	0.40	<10	1.50	410	<2	0.08	146	877	30	0.04	<5	4	88	<5	0.15	<10	<10	82	<10	32	3
46728	<0.2	1.67	6	263	<0.5	<5	1.65	1	21	80	8	3.63	<1	0.75	10	2.34	339	<2	0.10	55	2429	14	0.03	<5	4	95	<5	0.22	<10	<10	104	<10	33	5
46736	<0.2	2.76	7	<10	<0.5	<5	1.02	<1	48	272	25	4.01	<1	0.03	<10	7.71	642	<2	0.01	880	432	36	0.25	<5	4	43	<5	0.03	<10	<10	62	<10	38	2
46737	<0.2	1.79	9	<10	<0.5	<5	0.32	<1	59	330	14	3.73	<1	0.02	<10	6.81	539	<2	0.01	1054	303	10	0.16	6	3	27	<5	0.02	<10	<10	35	<10	28	2

A .5 gm sample is digested with 5 ml 3:1 HCl/HNO3 at 95°C for 2 hours and diluted to 25ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V3790RJ

Date : Nov-13-08

WHY Resources

Attention: Frank Maraso

Project: Record Ridge South

Sample type: drill core

Multi-Element ICP-AES Analysis

Aqua Regia Digestion

Sample Number	Ag ppm	Al %	As ppm	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	Hg ppm	K %	La ppm	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	S %	Sb ppm	Sc ppm	Sr ppm	Th ppm	Ti %	Tl ppm	U ppm	V ppm	W ppm	Zn ppm	Zr ppm
46738	<0.2	1.98	8	<10	<0.5	<5	1.29	2	61	305	14	4.51	<1	0.02	<10	6.53	1135	<2	0.01	906	293	120	0.32	6	7	47	<5	0.03	<10	10	68	<10	324	2
46739	<0.2	3.39	<5	127	<0.5	<5	0.62	1	31	41	11	5.96	<1	0.91	<10	4.17	1672	<2	0.04	48	1280	27	0.17	<5	23	30	<5	0.16	<10	10	198	<10	140	3
46740	<0.2	2.79	<5	12	<0.5	<5	0.39	<1	36	216	2	4.01	<1	0.14	<10	5.51	700	<2	0.01	402	588	18	0.07	<5	7	19	<5	0.07	<10	<10	111	<10	54	2
46752	<0.2	2.68	5	122	<0.5	<5	1.14	1	24	25	28	4.68	1	0.74	<10	2.80	484	<2	0.12	31	1158	18	0.01	<5	4	102	<5	0.19	<10	<10	200	<10	46	4
46753	<0.2	2.76	5	99	<0.5	<5	2.51	1	28	178	12	4.53	<1	0.72	<10	2.43	519	<2	0.18	235	919	16	0.01	5	4	125	<5	0.19	<10	<10	170	<10	42	5
46754	<0.2	2.76	5	111	<0.5	<5	1.26	1	25	14	5	5.17	1	0.97	<10	1.98	499	<2	0.21	13	1041	19	<0.01	<5	6	110	<5	0.22	<10	<10	227	<10	48	5
46755	<0.2	2.02	5	59	<0.5	<5	1.78	1	23	22	5	4.43	1	0.55	<10	1.37	483	<2	0.20	27	1147	14	<0.01	<5	5	109	<5	0.24	<10	<10	185	<10	39	5
46756	<0.2	2.33	5	58	<0.5	<5	1.35	1	30	290	6	4.56	<1	0.80	<10	2.84	456	<2	0.13	291	820	14	<0.01	7	4	69	<5	0.20	<10	<10	148	<10	46	4
46757	<0.2	2.25	<5	<10	<0.5	<5	0.45	<1	40	742	12	3.67	<1	0.07	<10	4.56	339	<2	0.02	668	290	14	0.01	11	1	8	<5	0.07	<10	<10	52	<10	29	3
46758	<0.2	1.84	<5	46	<0.5	<5	1.15	1	27	217	4	4.37	<1	0.38	<10	2.18	415	<2	0.09	183	950	11	<0.01	<5	2	55	<5	0.18	<10	<10	143	<10	38	4
46759	<0.2	1.58	<5	40	<0.5	<5	1.24	1	24	40	10	4.59	1	0.29	<10	1.64	507	<2	0.07	39	1195	13	<0.01	<5	4	65	<5	0.21	<10	<10	170	<10	42	5
46760	<0.2	1.33	<5	23	<0.5	<5	2.19	1	21	19	7	4.50	<1	0.17	<10	1.42	564	<2	0.06	15	1242	21	<0.01	<5	5	73	<5	0.17	<10	<10	163	<10	44	4
46761	<0.2	3.11	<5	85	<0.5	<5	0.80	1	33	323	21	4.46	<1	0.53	<10	4.62	543	<2	0.10	328	796	20	<0.01	6	4	57	<5	0.15	<10	<10	134	<10	45	4
46762	<0.2	1.84	6	57	<0.5	<5	1.38	1	24	33	17	4.59	1	0.71	<10	1.47	494	<2	0.15	20	1173	16	<0.01	<5	5	107	<5	0.24	<10	<10	188	<10	48	6
46763	<0.2	1.80	8	48	<0.5	<5	2.27	1	24	17	14	4.40	1	0.47	<10	1.54	631	<2	0.12	10	1109	16	0.02	<5	6	112	<5	0.25	<10	<10	179	<10	57	6
46764	<0.2	1.92	9	103	<0.5	<5	1.55	1	25	22	36	4.26	<1	0.81	<10	1.78	470	<2	0.12	14	1125	14	0.01	<5	6	96	<5	0.22	<10	<10	151	<10	50	5
46765	<0.2	2.36	6	129	<0.5	<5	1.90	1	28	57	29	5.07	<1	0.85	<10	2.28	558	<2	0.13	57	1554	17	0.02	<5	7	76	<5	0.24	<10	<10	182	<10	54	6
46766	<0.2	2.05	7	246	<0.5	<5	1.31	1	28	47	43	4.94	<1	1.13	<10	2.18	487	<2	0.13	46	1434	15	0.02	<5	6	84	<5	0.25	<10	<10	200	<10	49	6
46767	<0.2	2.63	9	515	<0.5	<5	1.72	1	37	163	49	4.89	<1	1.70	<10	3.51	631	<2	0.14	141	2036	28	0.04	5	5	121	6	0.26	<10	<10	160	<10	59	11
46768	<0.2	1.92	6	109	<0.5	<5	1.22	1	25	19	57	4.91	1	0.77	<10	1.60	423	<2	0.15	8	1236	14	0.01	<5	6	107	<5	0.25	<10	<10	214	<10	44	5
46769	<0.2	2.00	6	93	<0.5	<5	1.67	1	25	18	47	4.62	1	0.73	<10	1.52	449	<2	0.19	10	1189	16	0.02	<5	7	100	<5	0.27	<10	<10	201	<10	38	5
46770	<0.2	1.93	7	27	<0.5	<5	3.49	1	23	19	36	4.41	1	0.29	<10	1.40	738	<2	0.13	10	1169	16	0.07	<5	9	134	<5	0.26	<10	<10	197	<10	36	5
46771	<0.2	1.79	5	43	<0.5	<5	2.03	1	26	13	7	4.69	<1	0.37	<10	1.71	591	<2	0.09	6	1169	13	0.01	<5	8	107	<5	0.27	<10	<10	194	<10	44	5
46772	<0.2	1.68	5	19	<0.5	<5	1.92	1	23	18	12	4.14	<1	0.12	<10	1.52	498	<2	0.06	7	1212	29	0.03	<5	6	113	<5	0.24	<10	<10	150	<10	44	4
46773	<0.2	1.98	7	46	<0.5	<5	1.77	1	25	24	13	4.46	<1	0.46	<10	1.32	445	<2	0.17	18	1101	19	0.01	<5	7	111	<5	0.28	<10	<10	196	<10	37	5
46774	<0.2	1.90	5	34	<0.5	<5	1.85	1	24	19	3	4.68	1	0.31	<10	1.40	460	<2	0.15	8	1171	26	<0.01	<5	6	106	<5	0.25	<10	<10	191	<10	40	4
46775	<0.2	2.68	5	53	<0.5	<5	2.00	1	23	17	14	4.67	1	0.64	<10	1.07	370	<2	0.32	12	1189	21	<0.01	<5	8	105	<5	0.27	<10	<10	217	<10	29	4
46776	<0.2	2.98	7	57	<0.5	<5	2.18	1	22	32	18	4.42	1	0.93	<10	1.15	371	<2	0.27	15	1132	24	0.06	<5	10	84	<5	0.21	<10	<10	213	<10	35	3
46777	0.2	2.23	7	43	<0.5	<5	2.44	1	31	13	114	5.50	1	0.37	<10	1.95	1185	<2	0.11	8	1172	268	0.21	<5	10	136	<5	0.32	<10	<10	213	<10	161	6
46778	<0.2	2.16	7	49	<0.5	<5	2.08	1	27	13	14	5.27	1	0.44	<10	1.52	573	<2	0.11	5	1184	47	0.09	<5	8	116	<5	0.30	<10	<10	208	<10	59	5

A .5 gm sample is digested with 5 ml 3:1 HCl/HNO3 at 95°C for 2 hours and diluted to 25ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V3790RJ

Date : Nov-13-08

WHY Resources

Attention: Frank Maraso

Project: Record Ridge South

Sample type: drill core

Multi-Element ICP-AES Analysis

Aqua Regia Digestion

Sample Number	Ag ppm	Al %	As ppm	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	Hg ppm	K %	La ppm	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	S %	Sb ppm	Sc ppm	Sr ppm	Th ppm	Ti %	Tl ppm	U ppm	V ppm	W ppm	Zn ppm	Zr ppm
46779	<0.2	1.85	5	29	<0.5	<5	2.28	1	26	17	17	4.94	1	0.25	<10	1.55	627	<2	0.11	8	1092	36	0.02	<5	8	99	<5	0.29	<10	<10	203	<10	59	5
Duplicates:																																		
46701	1.0	2.22	15	150	<0.5	<5	2.69	2	28	184	50	3.70	<1	0.36	<10	2.29	1200	<2	0.06	328	987	78	0.11	6	5	154	<5	0.13	<10	<10	61	<10	187	6
46710	<0.2	2.67	<5	85	<0.5	<5	1.03	1	20	45	7	3.33	1	1.14	<10	1.85	228	<2	0.19	34	771	18	<0.01	<5	9	67	<5	0.14	<10	<10	128	<10	17	3
46720	1.5	2.26	9	365	<0.5	<5	0.93	1	52	266	54	3.84	<1	1.27	<10	4.15	389	<2	0.07	685	1669	28	0.02	7	4	63	<5	0.17	<10	<10	80	<10	35	12
46723	1.4	2.60	12	166	<0.5	<5	3.28	1	20	33	33	3.98	<1	0.84	<10	2.68	626	<2	0.09	58	843	23	0.02	<5	5	147	<5	0.14	<10	<10	101	<10	25	4
46739	<0.2	3.40	<5	125	<0.5	<5	0.64	1	32	41	13	5.97	<1	0.90	<10	4.15	1693	<2	0.04	48	1285	28	0.18	<5	23	29	<5	0.19	<10	10	199	<10	136	4
46760	<0.2	1.33	5	21	<0.5	<5	2.13	1	21	19	6	4.30	1	0.16	<10	1.35	534	<2	0.06	14	1171	19	<0.01	<5	5	73	<5	0.20	<10	<10	158	<10	39	4
46763	<0.2	1.93	9	49	<0.5	<5	2.49	1	26	18	13	4.74	1	0.47	<10	1.56	651	<2	0.13	10	1139	18	0.02	<5	6	117	<5	0.27	<10	<10	184	<10	57	6
46772	<0.2	1.71	5	18	<0.5	<5	2.00	1	24	18	11	4.24	<1	0.13	<10	1.54	507	<2	0.06	8	1242	30	0.03	<5	6	116	<5	0.25	<10	<10	153	<10	46	4
Standards:																																		
Blank	<0.2	<0.01	<5	<10	<0.5	<5	<0.01	<1	<1	<1	<1	<0.01	<1	<0.01	<10	<0.01	<5	<2	0.01	<1	<10	<2	<0.01	<5	<1	<1	<5	<0.01	<10	<10	<1	<10	<1	<1
ICP-2	0.6	1.59	61	161	<0.5	<5	4.16	3	85	188	1142	6.21	1	0.23	17	1.52	1740	6	0.03	96	1313	71	2.06	<5	7	453	<5	0.02	<10	<10	116	<10	324	11

A .5 gm sample is digested with 5 ml 3:1 HCl/HNO3 at 95°C for 2 hours and diluted to 25ml.

**Assayers Canada**

8282 Sherbrooke St.
Vancouver, B.C.
V5X 4R6
Tel: (604) 327-3436
Fax: (604) 327-3423

Quality Assaying for over 25 Years

Assay Certificate**8V-2181-RA1**

Company: **Why Resources**
Project: Record Ridge South
Attn: Frank Marasco

Nov-19-08

We hereby certify the following assay of 24 drill core samples
submitted Jun-11-08

Sample Name	Cr %	Fe %	Fe3O4 %	SiO2 %
43451	0.24	4.50	3.86	41.7
43452	0.31	6.21	6.00	45.6
43453	1.95	6.94	6.98	45.4
43454	0.34	4.25	3.18	29.2
43455	0.27	4.94	4.10	33.0
43456	0.26	5.24	4.48	36.9
43457	0.26	4.81	4.09	36.2
43458	0.31	5.04	4.81	38.3
43459	0.18	5.44	3.77	31.7
43460	0.18	4.69	4.82	31.1
43461	0.19	3.89	3.63	19.0
43465	0.33	5.49	5.73	28.9
43466	<0.01	7.59	4.33	45.0
43467	0.28	4.54	4.15	34.2
43468	0.31	4.18	3.36	25.9
43469	0.34	5.47	4.71	26.8
43470	0.41	5.52	4.91	22.5
43471	0.29	3.86	3.10	26.7
43472	0.15	3.43	3.84	29.3
43473	0.07	3.65	3.18	44.5
43474	0.23	4.47	3.92	30.2
43475	0.28	4.50	3.48	45.3
43476	0.34	4.93	3.45	39.0
43477	0.29	5.47	4.82	30.1
*DUP 43451	0.26	4.78		39.6
*DUP 43460	0.16	4.35		33.8
*DUP 43473	0.06	3.70		42.1
*RTS-1		18.9		42.5
*K2CrO4	25.4			
*BLANK	<0.01	<0.01	<0.01	<0.01

Certified by _____



Assayers Canada
8282 Sherbrooke St.
Vancouver, B.C.
V5X 4R6
Tel: (604) 327-3436
Fax: (604) 327-3423

Quality Assaying for over 25 Years

Assay Certificate

8V-2181-RA2

Company: **Why Resources**
Project: Record Ridge South
Attn: Frank Marasco

Nov-19-08

We hereby certify the following assay of 24 drill core samples
submitted Jun-11-08

Sample Name	Cr %	Fe %	Fe3O4 %	SiO2 %
43478	0.29	6.26	5.82	44.3
43479	0.36	5.86	5.20	56.9
43480	0.37	5.25	4.04	34.0
43481	0.28	5.82	5.17	35.3
43482	0.40	6.30	6.01	39.8
43483	0.22	4.29	3.19	24.2
43484	0.28	5.15	4.20	34.0
43485	0.35	4.64	3.68	34.4
43486	0.32	4.69	3.40	34.2
43487	0.27	5.65	4.57	44.5
43488	0.29	4.59	2.72	32.0
43489	0.31	4.70	3.29	36.3
43490	0.32	5.39	4.16	30.9
43491	0.29	4.98	3.79	33.5
43492	0.38	5.07	4.16	41.0
43493	0.29	4.47	3.76	41.8
43497	0.21	4.34	2.79	30.9
43498	0.25	4.22	2.82	38.3
43499	0.28	5.13	4.80	47.9
43501	0.80	6.71	6.77	45.9
43506	0.30	4.74	3.25	35.6
43507	0.25	5.27	3.86	26.2
43508	0.32	5.32	4.02	23.7
43509	0.24	4.82	3.28	29.5
*DUP 43478	0.27	6.10		42.3
*DUP 43487	0.25	5.46		44.5
*DUP 43501	0.75	6.75		46.7
*RTS-1		20.2		43.6
*K2CrO4	26.0			
*BLANK	<0.01	<0.01	<0.01	<0.01

Certified by _____



Assayers Canada
8282 Sherbrooke St.
Vancouver, B.C.
V5X 4R6
Tel: (604) 327-3436
Fax: (604) 327-3423

Quality Assaying for over 25 Years

Assay Certificate

8V-2181-RA3

Company: **Why Resources**
Project: Record Ridge South
Attn: Frank Marasco

Nov-19-08

We hereby certify the following assay of 24 core samples
submitted Jun-11-08

Sample Name	Cr %	Fe %	Fe3O4 %	SiO2 %
43510	0.29	5.89	5.35	41.9
43511	0.35	7.64	7.57	27.6
43512	0.28	6.13	5.64	29.5
43513	0.54	4.44	3.48	30.0
43514	0.29	3.75	2.20	29.0
43515	0.27	4.33	2.92	31.1
43516	0.29	4.48	4.01	39.4
43518	0.30	3.86	2.43	30.1
43519	0.30	4.15	3.21	30.3
43520	0.23	5.26	4.52	40.5
43521	0.20	3.28	1.77	29.1
43522	0.30	3.52	2.32	31.1
43523	0.15	4.82	3.30	25.3
43524	0.26	4.47	3.28	48.9
43526	0.20	3.47	2.14	27.1
43527	0.22	3.46	2.13	25.8
43528	0.29	3.71	2.42	27.1
43529	0.33	5.01	4.30	37.4
43530	0.18	3.05	1.76	23.9
43531	0.25	5.52	5.03	35.4
43532	0.46	5.05	4.71	34.2
43533	0.27	4.96	4.21	34.9
43534	0.29	4.96	4.55	34.3
43535	0.28	4.09	3.34	30.3
*DUP 43510	0.32	5.98		40.1
*DUP 43520	0.24	5.10		39.5
*DUP 43531	0.24	5.48		34.0
*MRG-1		12.6		40.1
*K2CrO4	26.1			
*BLANK	<0.01	<0.01	<0.01	<0.01

Certified by _____



Assayers Canada
8282 Sherbrooke St.
Vancouver, B.C.
V5X 4R6
Tel: (604) 327-3436
Fax: (604) 327-3423

Quality Assaying for over 25 Years

Assay Certificate

8V-2181-RA4

Company: **Why Resources**
Project: Record Ridge South
Attn: Frank Marasco

Nov-19-08

We hereby certify the following assay of 24 core samples
submitted Jun-11-08

Sample Name	Cr %	Fe %	Fe3O4 %	SiO2 %
43536	0.27	5.38	4.93	38.0
43537	0.49	6.02	5.32	41.5
43538	0.23	4.79	3.66	39.0
43539	0.34	5.53	4.55	39.4
43540	0.29	5.54	4.34	42.6
43541	0.29	5.70	5.06	34.3
43542	0.27	7.21	7.86	48.4
43543	0.32	4.85	4.19	40.6
43544	0.28	5.23	4.37	36.4
43545	0.29	6.35	6.55	43.5
43546	0.36	5.14	4.62	31.4
43547	0.32	5.40	4.37	39.7
43548	0.15	5.84	4.60	40.3
43549	0.26	5.37	4.84	38.6
43550	0.38	5.40	4.75	37.6
43553	0.25	5.46	5.21	46.2
43554	0.39	5.40	4.30	34.5
43555	0.30	6.14	5.28	41.9
43556	0.25	4.66	3.73	32.5
43557	0.23	4.44	3.90	34.1
43561	0.21	6.42	5.67	44.1
43562	0.31	6.82	6.22	41.0
43563	0.43	6.70	5.25	41.7
43564	0.32	7.44	7.70	42.7
*DUP 43536	0.25	5.56		39.0
*DUP 43545	0.31	6.43		41.1
*DUP 43557	0.19	4.64		33.1
*RTS-1		19.1		42.9
*K2CrO4	25.9			
*BLANK	<0.01	<0.01	<0.01	<0.01

Certified by _____



Assayers Canada
8282 Sherbrooke St.
Vancouver, B.C.
V5X 4R6
Tel: (604) 327-3436
Fax: (604) 327-3423

Quality Assaying for over 25 Years

Assay Certificate

8V-2181-RA5

Company: **Why Resources**
Project: Record Ridge South
Attn: Frank Marasco

Nov-19-08

We hereby certify the following assay of 24 core samples
submitted Jun-11-08

Sample Name	Cr %	Fe %	Fe3O4 %	SiO2 %
43565	0.34	7.22	8.14	39.6
43566	0.65	6.63	6.85	43.7
43567	0.39	6.34	6.36	51.0
43570	0.34	5.42	4.95	43.0
43571	0.36	5.71	5.54	40.1
43572	0.54	8.53	8.98	41.5
43573	0.29	5.69	5.00	41.1
43574	0.42	5.16	4.44	37.2
43575	0.36	4.94	4.04	34.6
43576	0.33	6.37	6.03	48.8
43577	0.48	6.70	6.47	44.9
43578	0.35	6.18	5.80	45.2
43579	0.38	5.73	5.32	41.0
43580	0.28	6.07	5.65	47.0
43581	0.29	4.58	3.47	32.1
43582	0.37	5.73	5.36	50.8
43583	0.34	6.46	6.25	50.5
43584	0.39	5.51	4.88	44.2
43585	0.26	5.06	4.05	49.3
43586	0.25	6.16	5.15	49.4
43588	0.31	4.84	4.24	46.0
43589	0.24	4.53	3.61	38.7
43590	0.25	5.22	4.77	40.6
43591	0.28	5.01	4.23	38.6
*DUP 43565	0.32	7.66		41.9
*DUP 43576	0.32	6.85		47.8
*DUP 43586	0.21	6.11		47.1
*RTS-1		19.9		43.5
*K2CrO4	26.4			
*BLANK	<0.01	<0.01	<0.01	<0.01

Certified by _____



Assayers Canada
8282 Sherbrooke St.
Vancouver, B.C.
V5X 4R6
Tel: (604) 327-3436
Fax: (604) 327-3423

Quality Assaying for over 25 Years

Assay Certificate

8V-2181-RA6

Company: **Why Resources**
Project: Record Ridge South
Attn: Frank Marasco

Nov-19-08

We hereby certify the following assay of 24 core samples
submitted Jun-11-08

Sample Name	Cr %	Fe %	Fe3O4 %	SiO2 %
43592	0.22	5.41	4.86	44.1
43593	0.25	6.30	6.38	49.1
43594	0.32	7.80	8.24	50.1
43595	0.24	6.92	7.50	46.8
43596	0.27	7.84	8.48	54.5
43597	0.28	6.81	6.95	47.1
43598	0.22	7.09	7.14	49.2
43599	0.25	5.75	5.75	53.3
43600	0.21	5.40	5.02	42.3
43601	0.05	7.93	5.38	54.8
43602	0.34	6.33	6.07	46.4
43603	0.30	7.11	7.14	48.9
43604	0.24	5.04	4.10	32.3
43605	0.22	6.00	5.36	35.6
43606	0.26	4.75	3.45	31.2
43607	0.24	6.59	5.71	50.6
*DUP 43592	0.21	5.32		43.5
*DUP 43601	0.04	8.05		52.0
*RTS-1		19.0		42.9
*K2CrO4	25.8			
*BLANK	<0.01	<0.01	<0.01	<0.01

Certified by _____



Assayers Canada
8282 Sherbrooke St.
Vancouver, B.C.
V5X 4R6
Tel: (604) 327-3436
Fax: (604) 327-3423

Quality Assaying for over 25 Years

Assay Certificate

8V-2181-RA7

Company: **Why Resources**
Project: Record Ridge South
Attn: Frank Marasco

Nov-19-08

We *hereby certify* the following assay of 24 drill core samples
submitted Jun-11-08

**Sample
Name**

Certified by _____

**Assayers Canada**

8282 Sherbrooke St.
Vancouver, B.C.
V5X 4R6
Tel: (604) 327-3436
Fax: (604) 327-3423

Quality Assaying for over 25 Years

Assay Certificate**8V-2217-RA1**

Company: **WHY Resources**
Project: Record Ridge South
Attn: Frank Marasco

Nov-20-08

We hereby certify the following assay of 24 rock samples
submitted Jun-13-08

Sample Name	Cr %	Fe %	Fe3O4 %	SiO2 %
43608	0.26	6.18	5.68	32.7
43609	0.39	5.59	4.73	42.1
43610	0.37	6.31	5.38	46.3
43611	0.33	5.34	4.17	40.6
43612	0.35	6.21	5.58	44.2
43613	0.33	4.95	3.90	35.0
43614	0.33	5.90	5.35	39.6
43615	0.26	5.07	4.63	46.9
43616	0.45	6.28	6.14	42.8
43617	0.12	8.12	4.49	33.9
43618	0.38	5.73	5.28	42.4
43619	0.29	6.61	6.44	41.0
43620	0.54	5.68	5.25	40.5
43621	0.34	5.28	4.89	37.8
43622	0.34	6.03	6.05	45.8
43623	0.47	6.87	7.32	36.9
43624	0.34	5.43	5.27	42.1
43625	0.37	6.06	6.07	41.2
43626	0.30	5.30	4.71	36.6
43627	0.34	5.53	4.89	38.2
43628	0.29	4.91	4.27	31.5
43629	0.30	5.03	4.46	34.0
43630	0.41	5.61	5.40	38.9
43631	0.50	6.46	6.25	43.2
*DUP 43608	0.26	6.41		34.5
*DUP 43617	0.12	7.70		31.8
*DUP 43627	0.33	5.26		36.2
*MRG-1		12.6		38.2
*K2CrO4	25.9			
*BLANK	<0.01	<0.01	<0.01	<0.01

Certified by _____



Assayers Canada
8282 Sherbrooke St.
Vancouver, B.C.
V5X 4R6
Tel: (604) 327-3436
Fax: (604) 327-3423

Quality Assaying for over 25 Years

Assay Certificate

8V-2217-RA2

Company: **WHY Resources**
Project: Record Ridge South
Attn: Frank Marasco

Nov-20-08

We hereby certify the following assay of 24 rock samples
submitted Jun-13-08

Sample Name	Cr %	Fe %	Fe3O4 %	SiO2 %
43632	0.27	6.27	5.90	44.2
43633	0.27	6.16	5.36	46.7
43634	0.38	5.47	4.71	41.0
43635	0.33	4.09	2.62	41.8
43636	0.34	5.86	5.43	39.8
43637	0.48	5.67	5.15	41.2
43638	0.30	6.65	6.69	44.2
43639	0.02	6.34	4.50	62.5
43640	0.33	5.99	5.68	43.8
43641	0.22	4.99	4.28	38.6
43642	0.24	5.13	4.26	38.8
43643	0.26	5.63	5.24	40.0
43644	0.36	5.56	5.04	40.4
43645	0.25	5.75	5.24	54.1
43646	0.29	5.16	4.34	42.6
43655	0.24	5.17	4.57	44.2
43656	0.22	5.45	4.50	44.2
43657	0.23	5.99	4.62	44.7
43658	0.07	11.8	5.83	31.9
43659	0.21	5.32	4.37	47.8
43660	0.26	5.52	4.74	43.8
43661	0.28	5.54	5.02	40.4
43662	0.24	4.81	3.37	39.1
43663	0.26	5.60	4.42	44.5
*DUP 43632	0.27	6.08		42.5
*DUP 43641	0.24	5.27		40.3
*DUP 43659	0.22	5.29		49.9
*RTS-1		19.7		43.8
*K2CrO4	25.9			
*BLANK	<0.01	<0.01	<0.01	<0.01

Certified by _____



Assayers Canada
8282 Sherbrooke St.
Vancouver, B.C.
V5X 4R6
Tel: (604) 327-3436
Fax: (604) 327-3423

Quality Assaying for over 25 Years

Assay Certificate

8V-2217-RA3

Company: **WHY Resources**
Project: Record Ridge South
Attn: Frank Marasco

Nov-20-08

We hereby certify the following assay of 24 rock samples
submitted Jun-13-08

Sample Name	Cr %	Fe %	Fe3O4 %	SiO2 %
43664	0.30	6.52	5.89	46.1
43665	0.32	6.91	6.19	45.7
43666	0.19	4.14	3.80	39.7
43667	0.44	5.24	3.99	36.9
43668	0.38	5.07	3.55	36.0
43669	0.41	4.81	3.23	33.4
43670	0.35	4.60	3.21	41.6
43671	0.41	4.98	3.75	36.3
43672	0.40	5.43	4.20	41.0
43673	0.28	6.35	5.38	44.5
43674	0.30	5.00	3.50	39.8
43675	0.39	5.35	4.55	33.8
43678	0.36	5.40	4.20	41.1
43679	0.35	5.01	3.50	40.8
43680	0.37	5.61	4.23	50.4
43681	0.34	4.57	2.82	40.7
43682	0.23	3.91	1.93	34.5
43683	0.31	5.16	3.59	47.8
43684	0.38	5.70	4.06	42.8
43685	0.31	6.09	4.66	39.2
43686	0.32	4.39	2.47	37.7
43687	0.30	5.09	3.75	43.4
43688	0.34	5.59	4.33	41.8
43689	0.13	5.20	4.46	34.6
*DUP 43664	0.29	6.24		44.2
*DUP 43673	0.30	6.30		44.0
*DUP 43685	0.30	5.71		41.1
*RTS-1		19.5		43.2
*K2CrO4	25.7			
*BLANK	<0.01	<0.01	<0.01	<0.01

Certified by _____



Assayers Canada
8282 Sherbrooke St.
Vancouver, B.C.
V5X 4R6
Tel: (604) 327-3436
Fax: (604) 327-3423

Quality Assaying for over 25 Years

Assay Certificate

8V-2217-RA4

Company: **WHY Resources**
Project: Record Ridge South
Attn: Frank Marasco

Nov-20-08

We hereby certify the following assay of 14 rock samples
submitted Jun-13-08

Sample Name	Cr %	Fe %	Fe3O4 %	SiO2 %
43690	0.32	5.58	4.71	39.0
43691	0.33	7.68	7.37	37.5
43692	0.27	5.18	6.63	56.8
43693	0.26	4.55	6.00	52.6
43694	0.23	4.68	6.08	68.1
43695	0.38	6.43	5.44	51.8
43696	0.33	6.91	6.84	52.5
43697	0.24	4.66	3.79	42.5
43698	0.35	6.03	5.44	52.0
43699	0.33	4.99	4.09	42.3
43700	0.24	4.52	3.73	41.4
43701	0.33	5.88	5.11	52.9
43702	0.25	5.40	4.82	54.8
43703	0.27	5.20	5.25	64.4
*DUP 43690	0.32	5.67		41.5
*DUP 43699	0.31	5.08		44.6
*RTS-1		19.5		43.8
*K2CrO4	26.1			
*BLANK	<0.01	<0.01	<0.01	<0.01

Certified by _____



Assayers Canada
8282 Sherbrooke St.
Vancouver, B.C.
V5X 4R6
Tel: (604) 327-3436
Fax: (604) 327-3423

Quality Assaying for over 25 Years

Assay Certificate

8V-2217-RA5

Company: **WHY Resources**
Project: Record Ridge South
Attn: Frank Marasco

Nov-20-08

We *hereby certify* the following assay of 12 rock samples
submitted Jun-13-08

**Sample
Name**

Certified by _____

**Assayers Canada**

8282 Sherbrooke St.
Vancouver, B.C.
V5X 4R6
Tel: (604) 327-3436
Fax: (604) 327-3423

Quality Assaying for over 25 Years

Assay Certificate**8V-2246-RA1**

Company: **WHY Resources**
Project: Record Ridge South
Attn: Frank Marasco

Nov-20-08

We hereby certify the following assay of 24 drill core samples
submitted Jun-17-08

Sample Name	Cr %	Fe %	Fe3O4 %	SiO2 %
43706	0.19	3.52	3.14	42.0
43707	0.27	4.35	3.28	41.8
43708	0.33	6.21	6.26	41.1
43709	0.27	4.61	3.59	29.8
43710	0.27	5.45	4.82	33.9
43711	0.33	5.62	5.21	37.1
43712	1.16	5.77	5.47	30.5
43713	0.30	4.62	4.08	30.1
43714	0.39	4.29	3.39	30.3
43715	0.29	4.92	4.17	42.0
43716	0.27	4.38	3.33	30.6
43717	0.25	6.42	6.32	42.0
43718	0.24	5.69	5.02	38.4
43719	0.24	4.57	3.70	39.0
43720	0.33	5.07	4.01	35.1
43721	0.19	3.71	2.34	23.5
43722	0.28	4.94	4.05	33.0
43723	0.25	4.57	3.48	30.7
43724	0.29	5.30	4.48	35.5
43725	0.27	4.74	4.50	31.0
43726	0.25	4.04	3.11	27.7
43727	0.16	2.55	1.19	22.4
43728	<0.01	5.13	1.51	48.1
43729	<0.01	5.45	2.29	38.1
*DUP 43706	0.18	3.55		43.4
*DUP 43715	0.28	5.14		39.3
*DUP 43725	0.28	4.64		29.1
*RTS-1		19.1		42.6
*K2CrO4	25.6			
*BLANK	<0.01	<0.01	<0.01	<0.01

Certified by _____



Assayers Canada
8282 Sherbrooke St.
Vancouver, B.C.
V5X 4R6
Tel: (604) 327-3436
Fax: (604) 327-3423

Quality Assaying for over 25 Years

Assay Certificate

8V-2246-RA2

Company: **WHY Resources**
Project: Record Ridge South
Attn: Frank Marasco

Nov-20-08

We hereby certify the following assay of 24 drill core samples
submitted Jun-17-08

Sample Name	Cr %	Fe %	SiO2 %
43730	<0.01	6.31	39.5
43731	0.47	4.22	26.0
43732	0.45	4.75	23.7
43733	0.41	5.09	30.9
43734	0.62	5.43	31.8
43735	0.73	6.34	32.2
43736	0.61	6.23	25.6
43737	0.41	6.10	31.9
43738	0.46	6.60	40.9
43739	0.37	6.69	39.2
43740	0.33	6.04	29.9
43741	0.43	7.91	35.7
43742	0.41	5.65	30.8
43743	0.34	6.78	42.9
43744	0.30	5.69	37.3
43745	<0.01	5.98	44.2
43746	0.38	9.74	42.8
43747	0.51	7.85	43.4
43748	0.36	6.32	41.3
43749	0.47	6.26	38.9
43750	0.40	4.69	22.1
43751	0.34	7.07	44.8
43752	0.35	6.72	26.1
43753	0.36	7.40	45.6
*DUP 43730	<0.01	6.86	41.2
*DUP 43739	0.37	6.39	40.6
*DUP 43749	0.47	6.03	36.3
*RTS-1		20.0	42.4
*K2CrO4	25.7		
*BLANK	<0.01	<0.01	<0.01

Certified by _____



Assayers Canada
8282 Sherbrooke St.
Vancouver, B.C.
V5X 4R6
Tel: (604) 327-3436
Fax: (604) 327-3423

Quality Assaying for over 25 Years

Assay Certificate

8V-2246-RA3

Company: **WHY Resources**
Project: Record Ridge South
Attn: Frank Marasco

Nov-20-08

We hereby certify the following assay of 24 drill core samples
submitted Jun-17-08

Sample Name	Cr %	Fe %	Fe3O4 %	SiO2 %
43754	0.39	6.20	5.36	52.1
43755	0.39	5.15	4.34	54.3
43756	0.60	6.03	4.82	56.3
43757	0.38	5.30	3.62	48.8
43758	0.45	7.62	7.37	55.7
43759	0.34	5.18	3.90	39.7
43760	0.31	4.29	2.36	45.8
43761	0.49	5.58	4.82	49.8
43762	0.40	5.70	4.85	47.1
43763	0.28	5.57	4.88	47.1
43764	0.32	5.49	4.26	43.9
43765	0.30	5.73	4.52	48.9
43766	0.27	4.55	3.18	37.3
43767	0.25	4.49	3.65	37.8
43768	0.18	5.63	3.95	49.2
43769	0.09	5.68	3.39	41.7
43770	0.29	4.90	3.94	55.5
43771	0.21	4.11	2.69	37.6
43772	0.28	5.95	5.00	55.9
43773	0.34	5.74	5.39	47.5
43774	0.35	6.07	5.24	57.5
43775	0.31	5.35	4.02	47.3
43776	0.31	3.83	1.95	35.4
43777	0.47	7.38	6.87	67.2
*DUP 43754	0.37	6.62		49.4
*DUP 43763	0.27	5.72		45.2
*DUP 43773	0.34	5.89		46.9
*RTS-1		19.1		41.9
*K2CrO4	26.4			
*BLANK	<0.01	<0.01	<0.01	<0.01

Certified by _____



Assayers Canada
8282 Sherbrooke St.
Vancouver, B.C.
V5X 4R6
Tel: (604) 327-3436
Fax: (604) 327-3423

Quality Assaying for over 25 Years

Assay Certificate

8V-2246-RA4

Company: **WHY Resources**
Project: Record Ridge South
Attn: Frank Marasco

Nov-20-08

We hereby certify the following assay of 23 drill core samples
submitted Jun-17-08

Sample Name	Cr %	Fe %	Fe3O4 %	SiO2 %
43778	0.33	5.83	4.92	50.5
43779	0.34	4.93	3.61	40.8
43780	0.30	5.56	3.48	42.4
43781	0.38	5.29	3.87	37.0
43782	0.41	5.17	3.84	34.0
43783	0.45	5.88	5.13	35.3
43784	0.31	5.19	4.62	34.4
43785	0.24	5.07	4.57	30.1
43786	0.27	4.32	3.73	31.4
43787	0.30	5.55	5.46	34.6
43788	0.40	5.77	5.57	41.9
43789	0.49	4.78	4.42	38.9
43790	0.37	5.31	5.02	28.3
43791	0.30	4.83	4.48	26.8
43792	0.21	4.78	4.26	34.5
43793	0.31	4.72	3.87	36.9
43794	0.42	4.64	3.94	32.8
43795	0.42	4.99	4.46	34.0
43796	0.45	4.52	3.76	33.0
43797	0.47	5.56	4.89	38.1
43798	0.32	3.89	1.91	31.1
43799	0.29	4.72	2.32	46.6
43800	0.31	4.78	3.19	40.0
*DUP 43778	0.29	5.62		48.8
*DUP 43787	0.30	5.65		35.7
*DUP 43797	0.49	5.37		36.9
*RTS-1		20.3		42.2
*K2CrO4	26.0			
*BLANK	<0.01	<0.01	<0.01	<0.01

Certified by _____

**Assayers Canada**

8282 Sherbrooke St.

Vancouver, B.C.

V5X 4R6

Tel: (604) 327-3436

Fax: (604) 327-3423

Quality Assaying for over 25 Years

Assay Certificate**8V-2333-RA1**

Company: **WHY Resources**
Project: Record Ridge South
Attn: Frank Marasco

Jul-11-08

We *hereby certify* the following assay of 24 drill core samples
submitted Jun-25-08

Sample Name	ICP %

43801

43802

43817

43818

43819

43820

43821

43824

43825

43826

43827

43828

43829

43830

43831

43869

43870

43871

43872

43873

43874

43875

43876

43877

Certified by _____



Assayers Canada
8282 Sherbrooke St.
Vancouver, B.C.
V5X 4R6
Tel: (604) 327-3436
Fax: (604) 327-3423

Quality Assaying for over 25 Years

Assay Certificate

8V-2333-RA2

Company: **WHY Resources**
Project: Record Ridge South
Attn: Frank Marasco

Jul-11-08

We *hereby certify* the following assay of 10 drill core samples
submitted Jun-25-08

Sample Name	Au g/tonne

43878	
43879	
43880	
43881	
43882	
43883	
43884	
43885	
43886	
43887	

Certified by _____



Assayers Canada
8282 Sherbrooke St.
Vancouver, B.C.
V5X 4R6
Tel: (604) 327-3436
Fax: (604) 327-3423

Quality Assaying for over 25 Years

Assay Certificate

8V-2333-RA3

Page 1 of 2

Jul-11-08

Company: **WHY Resources**
Project: Record Ridge South
Attn: Frank Marasco

We hereby certify the following assay of 24 drill core samples
submitted Jun-25-08

Sample Name	Cr %	Fe %	Fe3O4 %	SiO2 %
43803	0.38	4.56	2.49	26.7
43804	0.37	4.15	2.31	31.3
43805	0.30	4.53	2.58	37.5
43806	0.33	4.45	3.84	36.9
43807	0.34	4.28	2.49	31.3
43808	0.33	4.32	2.39	21.1
43809	0.36	4.91	3.10	24.3
43810	0.31	4.55	2.74	28.8
43811	0.37	5.07	3.44	33.8
43812	0.30	4.57	3.10	29.1
43813	0.39	5.19	3.00	35.0
43814	0.28	4.96	3.01	35.0
43815	0.43	5.45	3.54	22.6
43816	0.32	4.94	3.03	36.4
43822	0.38	5.26	3.21	30.1
43823	0.38	5.77	3.76	33.0
43832	0.36	6.13	5.13	35.6
43833	0.26	5.12	3.74	30.1
43834	0.26	6.07	5.14	34.7
43835	0.29	4.74	3.03	25.4
43836	0.29	4.37	2.58	23.7
43837	0.23	3.79	1.93	21.6
43838	0.36	5.39	4.17	31.1
43839	0.34	5.59	4.08	25.2
*DUP 43803	0.39	4.44		26.7
*DUP 43812	0.30	4.26		29.3
*DUP 43835	0.30	4.83		33.8
*RTS-1		20.8		
*MRG-1				38.1
*K2CrO4	25.8			

Certified by _____



Assayers Canada
8282 Sherbrooke St.
Vancouver, B.C.
V5X 4R6
Tel: (604) 327-3436
Fax: (604) 327-3423

Quality Assaying for over 25 Years

Assay Certificate

8V-2333-RA3

Page 2 of 2

Jul-11-08

Company: **WHY Resources**
Project: Record Ridge South
Attn: Frank Marasco

We *hereby certify* the following assay of 24 drill core samples
submitted Jun-25-08

Sample Name	Cr %	Fe %	Fe3O4 %	SiO2 %
*BLANK	<0.01	<0.01	<0.01	<0.01

Certified by _____



Assayers Canada
8282 Sherbrooke St.
Vancouver, B.C.
V5X 4R6
Tel: (604) 327-3436
Fax: (604) 327-3423

Quality Assaying for over 25 Years

Assay Certificate

8V-2333-RA4

Company: **WHY Resources**
Project: Record Ridge South
Attn: Frank Marasco

Jul-11-08

We hereby certify the following assay of 24 drill core samples
submitted Jun-25-08

Sample Name	Cr %	Fe %	Fe3O4 %	SiO2 %
43840	0.29	5.62	4.27	26.6
43841	0.39	7.22	6.03	44.6
43842	0.47	6.56	5.51	33.7
43843	0.49	7.43	6.77	45.9
43844	0.44	7.95	7.46	42.5
43845	0.55	6.75	5.40	36.7
43846	0.38	6.98	5.47	40.7
43847	0.38	7.29	5.61	45.5
43848	0.36	7.75	6.15	49.3
43849	0.41	8.27	6.49	53.8
43850	0.35	7.16	5.36	40.9
43851	0.29	5.82	3.62	25.4
43852	0.40	7.46	5.93	44.5
43853	0.38	7.09	5.42	42.4
43854	0.33	6.87	4.89	31.3
43855	0.32	7.19	5.42	32.7
43856	0.27	6.39	4.26	28.7
43857	0.33	5.78	3.76	28.1
43858	0.27	5.76	3.70	27.8
43859	0.24	5.99	4.42	21.9
43860	0.27	6.30	5.46	25.2
43861	0.51	7.07	6.67	32.6
43862	0.26	4.84	3.29	21.1
43863	0.50	7.09	6.66	40.9
*DUP 43840	0.34	6.19		30.6
*DUP 43849	0.34	7.84		40.3
*DUP 43859	0.25	6.37		34.9
*RTS-1		20.4		41.7
*K2CrO4	25.6			
*BLANK	<0.01	<0.01	<0.01	<0.01

Certified by _____



Assayers Canada
8282 Sherbrooke St.
Vancouver, B.C.
V5X 4R6
Tel: (604) 327-3436
Fax: (604) 327-3423

Quality Assaying for over 25 Years

Assay Certificate

8V-2333-RA5

Company: **WHY Resources**
Project: Record Ridge South
Attn: Frank Marasco

Jul-11-08

We hereby certify the following assay of 24 drill core samples
submitted Jun-25-08

Sample Name	Cr %	Fe %	Fe3O4 %	SiO2 %
43864	0.32	5.40	3.87	36.9
43865	0.31	4.77	3.00	36.9
43866	0.26	4.78	2.21	33.6
43867	0.13	6.53	4.05	33.5
43868	0.15	8.52	7.19	59.3
43888	0.43	6.74	6.34	45.4
43889	0.53	7.00	6.74	50.0
43890	0.91	6.94	6.79	55.1
43891	1.02	7.01	6.98	46.4
43892	0.56	6.13	5.94	45.5
43893	0.92	7.19	7.59	50.9
43894	0.47	5.68	5.46	41.8
43895	0.41	6.17	6.12	44.4
43896	0.41	6.90	7.12	49.2
43897	0.27	6.68	6.68	50.5
43898	0.44	6.66	6.43	48.8
43899	0.15	5.81	5.11	35.4
43900	0.39	6.41	6.27	39.1
43901	0.60	5.33	4.92	34.1
43902	0.35	5.60	5.25	37.3
43903	0.20	5.32	4.74	42.0
43904	0.38	6.61	6.18	45.9
43905	0.60	6.11	5.36	47.2
43906	0.36	5.60	4.62	41.0
*DUP 43864	0.30	5.50		38.7
*DUP 43892	0.57	6.14		43.5
*DUP 43902	0.39	5.92		39.3
*MRG-1		12.3		39.0
*K2CrO4	26.7			
*BLANK	<0.01	<0.01	<0.01	<0.01

Certified by _____



Assayers Canada
8282 Sherbrooke St.
Vancouver, B.C.
V5X 4R6
Tel: (604) 327-3436
Fax: (604) 327-3423

Quality Assaying for over 25 Years

Assay Certificate

8V-2333-RA6

Company: **WHY Resources**
Project: Record Ridge South
Attn: Frank Marasco

Jul-11-08

We hereby certify the following assay of 24 drill core samples
submitted Jun-25-08

Sample Name	Cr %	Fe %	Fe3O4 %	SiO2 %
43907	0.28	4.79	3.73	28.4
43908	0.25	4.90	3.57	33.6
43909	0.32	5.36	4.26	32.7
43910	0.27	4.40	2.78	25.2
43911	0.33	4.63	2.60	29.3
43912	0.30	4.81	2.75	34.4
43913	0.25	3.88	1.44	30.3
43914	0.29	3.25	1.05	22.1
43915	0.03	3.59	1.12	33.4
43916	0.27	3.97	2.60	24.8
43917	0.24	4.86	4.13	30.9
43918	0.25	4.43	3.29	33.9
43919	0.22	4.21	3.12	29.1
43920	0.03	4.86	2.99	45.2
43921	0.28	4.85	3.58	33.5
43922	0.31	4.55	3.08	32.7
43923	0.25	4.87	3.63	32.1
43924	0.28	4.36	2.75	29.2
43925	0.16	3.92	3.18	31.2
43926	0.06	4.54	2.36	26.5
43927	0.19	3.34	2.56	31.7
43928	0.19	3.77	3.70	38.4
43929	0.20	4.30	3.14	29.8
43930	0.21	3.78	2.63	25.5
*DUP 43907	0.30	4.56		29.2
*DUP 43916	0.25	4.27		24.8
*DUP 43926	0.06	4.78		27.9
*RTS-1		19.6		43.3
*K2CrO4	25.3			
*BLANK	<0.01	<0.01	<0.01	<0.01

Certified by _____



Assayers Canada
8282 Sherbrooke St.
Vancouver, B.C.
V5X 4R6
Tel: (604) 327-3436
Fax: (604) 327-3423

Quality Assaying for over 25 Years

Assay Certificate

8V-2333-RA7

Company: **WHY Resources**
Project: Record Ridge South
Attn: Frank Marasco

Jul-11-08

We hereby certify the following assay of 24 drill core samples
submitted Jun-25-08

Sample Name	Cr %	Fe %	Fe3O4 %	SiO2 %
43931	0.21	5.63	5.79	49.9
43932	0.01	6.20	5.97	68.5
43933	0.28	5.49	5.56	63.2
43934	0.31	7.07	7.52	53.7
43935	0.42	6.75	7.13	47.4
43936	0.31	7.40	7.81	53.4
43937	0.26	5.60	5.39	44.0
43938	0.27	6.86	7.03	44.9
43939	0.29	6.26	6.05	46.5
43940	0.29	5.96	5.94	45.8
43941	0.30	6.79	6.79	54.2
43942	0.25	5.29	4.78	47.6
43943	0.27	5.06	4.37	47.0
43944	0.27	5.88	5.39	42.1
43945	0.34	6.05	5.73	42.7
43946	0.30	5.10	4.62	39.4
43947	0.25	5.63	5.62	42.5
43948	0.32	5.84	6.04	45.8
43949	0.26	5.70	5.76	47.9
43950	0.25	5.64	5.79	36.8
43951	0.42	6.13	6.47	44.8
43952	0.49	6.12	6.40	45.0
43953	0.46	5.82	5.98	44.7
43954	0.67	6.55	6.83	43.9
*DUP 43931	0.19	5.29		47.5
*DUP 43940	0.26	5.77		45.1
*DUP 43950	0.27	5.63		39.6
*MRG-1		12.3		40.0
*K2CrO4	27.4			
*BLANK	<0.01	<0.01	<0.01	<0.01

Certified by _____



Assayers Canada
8282 Sherbrooke St.
Vancouver, B.C.
V5X 4R6
Tel: (604) 327-3436
Fax: (604) 327-3423

Quality Assaying for over 25 Years

Assay Certificate

8V-2333-RA8

Company: **WHY Resources**
Project: Record Ridge South
Attn: Frank Marasco

Jul-11-08

We hereby certify the following assay of 24 drill core samples
submitted Jun-25-08

Sample Name	Cr %	Fe %	Fe3O4 %	SiO2 %
43955	0.51	5.29	4.71	32.1
43956	0.63	5.64	5.20	35.1
43957	0.43	5.54	4.97	36.7
43958	0.31	5.38	4.78	39.2
43959	0.34	5.40	4.74	32.0
43960	0.47	6.21	5.18	36.6
43961	0.64	6.30	5.33	41.1
43962	0.39	6.05	4.84	44.0
43963	0.73	6.93	5.85	34.4
43964	0.50	6.81	5.85	41.1
43965	0.44	6.18	4.81	40.9
43966	0.38	6.72	6.11	38.4
43967	0.52	5.43	4.24	29.6
43968	0.37	6.09	4.99	39.2
43969	0.36	6.72	5.85	52.3
43970	0.37	7.61	7.48	50.1
43971	0.25	5.40	4.70	36.3
43972	0.34	4.75	3.40	34.6
43973	0.27	7.10	6.58	52.0
43974	0.30	5.38	4.57	43.3
43975	0.35	6.20	5.53	49.1
43976	0.23	4.50	4.73	50.4
43977	0.05	7.31	4.67	53.3
43978	0.14	5.80	4.45	51.7
*01 DUP.	0.53	5.53		35.3
*10 DUP.	0.48	6.86		40.2
*20 DUP.	0.29	5.18		41.8
*RTS-1		19.1		42.9
*K2CrO4	25.4			
*BLANK	<0.01	<0.01	<0.01	<0.01

Certified by _____



Assayers Canada
8282 Sherbrooke St.
Vancouver, B.C.
V5X 4R6
Tel: (604) 327-3436
Fax: (604) 327-3423

Quality Assaying for over 25 Years

Assay Certificate

8V-2333-RA9

Company: **WHY Resources**
Project: Record Ridge South
Attn: Frank Marasco

Jul-11-08

We hereby certify the following assay of 24 drill core samples
submitted Jun-25-08

Sample Name	Cr %	Fe %	Fe3O4 %	SiO2 %
43979	0.33	4.94	4.27	28.3
43980	0.40	6.27	5.94	32.8
43981	0.34	5.49	4.53	32.8
43982	0.29	4.66	3.80	28.9
43983	0.43	4.78	4.12	30.9
43984	0.42	3.91	2.96	26.7
43985	0.20	5.85	3.57	37.5
43986	<0.01	5.41	1.80	46.0
43987	<0.01	4.52	1.91	31.4
43988	0.22	3.98	3.90	33.4
43989	0.30	4.68	3.73	30.8
43990	0.34	4.39	3.52	26.8
43991	0.20	3.92	2.87	16.8
43992	0.30	4.66	3.84	28.9
43993	0.20	3.52	2.38	20.5
43994	0.22	3.99	2.82	27.4
43995	0.28	4.21	3.12	23.6
43996	0.09	4.54	4.06	30.7
43997	0.11	4.94	4.20	35.5
43998	0.28	4.90	4.21	36.0
43999	0.23	4.43	3.14	36.2
44000	0.31	5.62	4.74	30.6
*DUP 43979	0.28	4.83		26.7
*DUP 43988	0.23	4.02		34.7
*DUP 43998	0.28	4.92		34.0
*RTS-1		19.5		42.0
*K2CrO4	25.5			
*BLANK	<0.01	<0.01	<0.01	<0.01

Certified by _____

**Assayers Canada**

8282 Sherbrooke St.

Vancouver, B.C.

V5X 4R6

Tel: (604) 327-3436

Fax: (604) 327-3423

Quality Assaying for over 25 Years

Assay Certificate**8V-2375-RA5**

Company: **WHY Resources**
Project: Record Ridge South
Attn: Frank Marasco

Nov-24-08

We *hereby certify* the following assay of 4 drill core samples
submitted Jul-02-08

Sample Name	Cr %	Fe %	Fe3O4 %	SiO2 %
044197	0.28	6.18	5.49	43.0
044198	0.45	6.42	6.69	39.0
044199	0.32	7.19	7.6	47.1
044200	0.41	8.95	10.1	50.1
*DUP 044197	0.27	6.12		45.3
*RTS-1		19.3		43.4
*K2CrO4	26.4			
*BLANK	<0.01	<0.01		<0.01

Certified by _____

**Assayers Canada**

8282 Sherbrooke St.

Vancouver, B.C.

V5X 4R6

Tel: (604) 327-3436

Fax: (604) 327-3423

Quality Assaying for over 25 Years

Assay Certificate**8V-2537-RA4**

Company: **WHY Resources**
Project: Record Ridge South
Attn: Frank Marasco

Nov-25-08

We hereby certify the following assay of 16 core samples
submitted Jul-14-08

Sample Name	Cr %	Fe %	Fe3O4 %	SiO2 %
44482	0.41	6.41	6.61	40.4
44483	0.46	6.97	7.20	45.1
44484	0.45	6.30	6.16	42.5
44485	0.37	4.77	3.86	37.7
44486	0.30	5.30	4.59	40.6
44487	0.27	4.65	3.91	41.9
44488	0.35	4.30	3.29	37.6
44489	0.32	3.96	2.99	39.7
44490	0.27	3.53	2.82	37.9
44491	0.22	4.41	4.85	48.6
44492	0.10	3.78	2.45	33.3
44493	0.02	5.20	2.69	46.2
44496	0.42	4.85	3.73	39.5
44497	0.28	4.04	2.43	37.1
44498	0.02	5.48	3.54	36.2
44499	<0.01	5.28	3.16	35.9
*DUP 44482	0.42	6.31		38.9
*DUP 44491	0.22	4.58		50.8
*RTS-1		19.7		42.1
*K2CrO4	25.5			
*BLANK	<0.01	<0.01	<0.01	<0.01

Certified by _____



Assayers Canada
8282 Sherbrooke St.
Vancouver, B.C.
V5X 4R6
Tel: (604) 327-3436
Fax: (604) 327-3423

Quality Assaying for over 25 Years

Assay Certificate

8V-2805-RA4

Company: **WHY Resources**
Project: Record Ridge South
Attn: Frank Marasco

Nov-28-08

We hereby certify the following assay of 20 core samples
submitted Jul-30-08

Sample Name	Cr %	Fe %	SiO2 %
44881	0.23	5.99	42.5
44882	0.25	6.34	45.5
44883	0.24	6.37	40.9
44884	0.21	6.46	42.3
44885	0.29	7.27	44.6
44886	0.30	7.43	49.9
44887	0.24	6.32	44.6
44888	0.26	6.05	46.5
44889	0.04	7.08	65.3
44890	0.02	6.99	57.6
44891	0.17	6.68	46.7
44892	0.27	5.64	41.7
44893	0.30	6.65	47.6
44894	0.28	6.64	45.0
44895	0.30	6.68	47.8
44896	0.21	5.90	40.6
44897	0.28	6.55	38.0
44898	0.23	5.96	39.7
44899	0.37	5.72	42.9
44900	0.42	5.86	41.2
*DUP 44881	0.26	5.94	41.1
*DUP 44890	0.02	6.60	57.5
*DUP 44900	0.41	5.81	42.0
*RTS-1		19.6	41.4
*K2CrO4	25.1		
*BLANK	<0.01	<0.01	<0.01

Certified by _____

**Assayers Canada**

8282 Sherbrooke St.

Vancouver, B.C.

V5X 4R6

Tel: (604) 327-3436

Fax: (604) 327-3423

Quality Assaying for over 25 Years

Assay Certificate**8V-3189-RA1**

Company: **WHY Resources**
Project: Record Ridge South
Attn: Frank Marasco

Sep-30-08

We *hereby certify* the following assay of 22 core samples
submitted Sep-02-08

**Sample
Name**

45601

45602

45603

45604

45605

45606

45607

45608

45609

45610

45611

45612

45613

45614

45615

45616

45617

45618

45619

45620

45621

45622

Certified by_____



Assayers Canada
8282 Sherbrooke St.
Vancouver, B.C.
V5X 4R6
Tel: (604) 327-3436
Fax: (604) 327-3423

Quality Assaying for over 25 Years

Assay Certificate

8V-3189-RA2

Company: **WHY Resources**
Project: Record Ridge South
Attn: Frank Marasco

Sep-30-08

We *hereby certify* the following assay of 22 drill core samples
submitted Sep-02-08

**Sample
Name**

45623
45624
45625
45626
45627
45628
45629
45630
45631
45632
45633
45634
45635
45636
45637
45638
45639
45640
45641
45642
45643
45644

Certified by_____



Assayers Canada
8282 Sherbrooke St.
Vancouver, B.C.
V5X 4R6
Tel: (604) 327-3436
Fax: (604) 327-3423

Quality Assaying for over 25 Years

Assay Certificate

8V-3189-RA3

Company: **WHY Resources**
Project: Record Ridge South
Attn: Frank Marasco

Sep-30-08

We hereby certify the following assay of 22 core samples
submitted Sep-02-08

Sample Name	Co %	Cr %	Mg %	Ni %	Ni-NiS ppm
45645					
45646					
45647					
45648					
45649					
45650					
45651					
45652					
45653					
45654					
45655					
45656					
45657					
45658					
45659					
45660					
45661					
45662					
45663					
45664					
45665					
45666	0.023	8.67	25.9	0.256	949
*MRG-1			8.11		
*RTS-2	0.009			0.244	237
*K2CrO4		25.9			
*BLANK	<0.001	<0.01	<0.01	<0.001	<1

Certified by _____



Assayers Canada
8282 Sherbrooke St.
Vancouver, B.C.
V5X 4R6
Tel: (604) 327-3436
Fax: (604) 327-3423

Quality Assaying for over 25 Years

Assay Certificate

8V-3189-RA4

Company: **WHY Resources**
Project: Record Ridge South
Attn: Frank Marasco

Sep-30-08

We hereby certify the following assay of 22 core samples
submitted Sep-02-08

Sample Name	Co %	Cr %	Mg %	Ni %	Ni-NiS ppm
45667	0.019	6.14	26.5	0.259	1068
45668	0.015	2.96	27.9	0.259	998
45669					
45670					
45671					
45672					
45673					
45674					
45675					
45676					
45677					
45678					
45679					
45680					
45681					
45682					
45683					
45684					
45685					
45686					
45687					
45688					
*MRG-1			8.14		
*RTS-2	0.008			0.241	242
*K2CrO4		26.1			
*BLANK	<0.001	<0.01	<0.01	<0.001	<1

Certified by _____



Assayers Canada
8282 Sherbrooke St.
Vancouver, B.C.
V5X 4R6
Tel: (604) 327-3436
Fax: (604) 327-3423

Quality Assaying for over 25 Years

Assay Certificate

8V-3189-RA5

Company: **WHY Resources**
Project: Record Ridge South
Attn: Frank Marasco

Sep-30-08

We hereby certify the following assay of 12 core samples
submitted Sep-02-08

Sample Name	Co %	Cr %	Mg %	Ni %	Ni-NiS ppm
45689	0.016	0.30	25.8	0.294	1296
45690	0.012	0.24	25.4	0.230	795
45691	0.013	0.22	19.5	0.241	1063
45692	0.011	0.30	26.1	0.221	1206
45693	0.015	0.38	31.3	0.326	1239
45694	0.015	0.39	29.4	0.315	1157
45695	0.008	0.24	25.8	0.172	1399
45696	0.016	0.50	27.5	0.310	1139
45697	0.009	0.20	20.0	0.170	791
45698	0.012	0.22	18.9	0.240	835
45699	0.006	0.21	9.94	0.073	95
45700					
*MRG-1			8.09		
*RTS-2	0.009			0.247	243
*K2CrO4		25.7			
*BLANK	<0.001	<0.01	<0.01	<0.001	<1

Certified by _____



Assayers Canada
8282 Sherbrooke St.
Vancouver, B.C.
V5X 4R6
Tel: (604) 327-3436
Fax: (604) 327-3423

Quality Assaying for over 25 Years

Assay Certificate

8V-3508-RA10

Company: **WHY Resources**
Project: Record Ridge South
Attn: Frank Marasco

Nov-06-08

We hereby certify the following assay of 8 core samples
submitted Sep-25-08

Sample Name	Au g/tonne	Pt g/tonne	Pd g/tonne
46358	0.01	0.01	<0.01
46359	0.01	0.01	<0.01
46370	0.01	0.01	0.01
46371	0.01	0.01	<0.01
46382 N.S.			
46383	<0.01	0.01	<0.01
46394	<0.01	0.01	<0.01
46395	0.01	0.01	<0.01
*DUP 46358	0.01	0.01	<0.01
*PtPd5	1.13	1.23	1.76
*BLANK	<0.01	<0.01	<0.01

Certified by _____

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2181RR

Date : Nov-19-08

Why Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
43451	<1	4.67	846	7.7	<5	1.85	2	68	1336	15	5.26	2.21	13.21	870	<2	1.70	1409	811	13	493	0.21	66	10	38
43452	<1	0.24	21	5.9	<5	0.92	3	137	3250	74	6.26	0.03	24.66	712	2	0.03	3208	41	15	67	0.01	18	10	<2
43453	<1	0.25	14	6.2	<5	1.54	3	134	6354	18	6.78	0.02	24.60	925	<2	0.02	2655	40	12	93	0.01	12	10	6
43454	<1	0.09	<10	5.1	<5	1.99	3	108	1749	17	6.05	0.01	25.86	747	<2	0.02	2383	32	13	62	<0.01	15	11	<2
43455	<1	0.12	<10	5.6	<5	1.54	2	94	1648	3	6.29	<0.01	25.28	809	<2	0.01	2338	32	7	32	<0.01	18	<10	2
43456	<1	0.13	<10	5.6	<5	1.91	2	106	1793	6	6.33	<0.01	26.40	890	<2	0.01	2463	33	8	28	<0.01	19	<10	7
43457	<1	0.11	<10	5.3	<5	2.52	2	92	1243	3	5.93	0.01	23.84	1026	<2	0.02	2285	41	7	37	<0.01	21	<10	3
43458	<1	0.10	11	4.9	<5	2.99	2	94	1347	22	5.60	<0.01	21.33	914	<2	0.02	2300	40	3	63	<0.01	20	<10	2
43459	<1	6.16	<10	6.0	<5	0.57	1	77	1518	119	6.69	0.01	18.67	429	<2	0.30	1229	635	13	21	0.30	198	10	<2
43460	<1	2.61	34	5.0	<5	4.41	1	76	1318	58	5.40	0.07	18.26	706	<2	0.06	1602	302	2	77	0.14	85	<10	11
43461	<1	0.10	<10	5.0	<5	6.19	2	99	1161	4	5.50	<0.01	19.97	1061	<2	0.01	2201	47	3	94	<0.01	18	<10	6
43465	<1	1.49	10	5.2	<5	6.30	2	94	1022	26	5.68	0.03	17.41	769	<2	0.06	1969	179	5	150	0.06	58	<10	9
43466	<1	10.21	384	7.2	<5	1.09	<1	48	56	7	7.47	2.09	7.62	915	<2	2.32	54	984	<2	285	0.47	308	10	46
43467	2	1.68	72	4.7	<5	7.49	2	87	999	267	5.17	0.32	14.38	875	3	0.26	1848	177	14	121	0.06	62	<10	24
43468	<1	0.06	<10	4.7	<5	3.21	2	107	1065	8	5.05	0.01	23.42	919	<2	0.01	2387	30	9	43	<0.01	13	<10	10
43469	<1	0.08	<10	4.9	<5	2.03	2	120	982	1	5.59	<0.01	23.91	705	<2	0.01	2359	32	6	40	<0.01	15	<10	8
43470	<1	0.35	<10	5.1	<5	1.39	2	109	1427	1	5.84	<0.01	25.01	725	<2	0.01	2380	55	6	21	0.02	22	<10	6
43471	<1	1.72	12	5.5	<5	3.44	2	90	825	70	5.94	0.01	20.97	740	2	0.01	1791	197	9	70	0.09	62	<10	16
43472	<1	0.35	<10	3.8	<5	2.77	2	77	871	11	4.30	<0.01	17.63	593	2	0.02	1797	61	29	52	0.02	21	<10	36
43473	<1	8.06	781	3.9	<5	0.70	2	51	426	28	3.81	1.66	9.93	2651	3	2.25	630	690	1220	208	0.22	110	10	474
43474	<1	3.71	173	4.7	<5	3.78	1	68	993	19	4.74	0.96	15.00	2670	11	0.07	1248	377	204	197	0.11	68	<10	214
43475	<1	0.15	15	3.6	<5	1.32	2	88	820	28	4.13	0.02	20.27	1155	2	0.04	1836	38	6	142	0.01	13	<10	40
43476	<1	0.07	<10	4.7	<5	0.73	2	113	1136	19	5.33	<0.01	23.35	1121	<2	0.01	2378	25	11	65	<0.01	15	<10	21
43477	<1	0.10	<10	5.4	<5	0.63	2	106	1907	16	6.14	<0.01	26.29	845	<2	0.01	2330	34	11	53	<0.01	14	11	<2
43478	<1	0.10	13	5.6	<5	0.54	3	104	1137	28	5.95	0.01	24.99	714	<2	0.01	2321	39	16	31	0.01	17	<10	<2
43479	<1	0.08	<10	5.4	<5	0.38	3	109	1262	24	6.02	0.01	26.10	678	<2	0.01	2282	32	19	21	<0.01	16	<10	<2
43480	<1	0.09	<10	5.2	<5	0.23	2	106	1366	14	5.75	<0.01	25.83	580	<2	0.01	2182	24	13	8	<0.01	16	<10	<2
43481	<1	0.06	13	6.1	<5	0.25	3	129	1128	20	6.77	<0.01	27.38	966	<2	0.01	2494	28	22	7	<0.01	17	<10	<2
43482	<1	0.06	<10	5.9	<5	0.12	3	141	1258	9	6.45	<0.01	26.49	726	<2	0.02	2480	37	15	4	<0.01	16	<10	<2
43483	<1	0.10	<10	6.3	<5	0.06	3	125	1889	2	6.97	<0.01	27.39	664	<2	0.02	2460	31	10	3	<0.01	15	<10	<2

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2181RR

Date : Nov-19-08

Why Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
43484	<1	0.05	<10	5.6	<5	0.22	3	149	1145	2	6.19	<0.01	28.66	899	<2	0.01	2456	29	13	10	<0.01	14	<10	<2
43485	<1	0.03	<10	4.8	<5	0.18	2	162	1127	3	5.30	<0.01	28.29	845	<2	0.01	2535	39	12	7	<0.01	12	<10	<2
43486	<1	0.05	<10	4.9	<5	0.19	3	141	1447	41	5.49	<0.01	27.27	745	<2	0.01	2346	27	11	5	<0.01	11	<10	<2
43487	<1	0.04	<10	5.0	<5	0.41	2	140	1158	44	5.57	0.01	28.47	860	<2	0.01	2615	38	11	6	<0.01	12	<10	<2
43488	<1	0.04	<10	5.1	<5	0.85	2	148	807	61	5.66	0.01	27.31	780	<2	0.02	2548	31	11	8	<0.01	14	<10	<2
43489	<1	0.06	<10	5.4	<5	1.15	2	142	1228	38	5.83	0.01	27.59	736	<2	0.02	2662	32	14	9	<0.01	16	<10	<2
43490	<1	0.93	<10	5.5	<5	1.94	2	98	1190	2	5.69	0.01	24.53	1008	<2	0.02	2251	103	8	40	0.04	35	<10	2
43491	<1	0.08	<10	6.2	<5	2.23	3	111	1389	<1	6.15	<0.01	25.72	1016	<2	0.03	2530	32	11	20	<0.01	18	<10	3
43492	<1	0.06	<10	5.6	<5	4.33	2	107	1264	<1	5.09	<0.01	23.35	1034	<2	0.02	2395	35	9	40	<0.01	16	<10	5
43493	<1	0.64	<10	4.7	<5	5.67	2	77	776	<1	4.57	<0.01	17.98	894	2	0.02	1696	124	18	99	0.02	25	<10	19
43497	<1	1.64	<10	5.3	<5	2.40	2	82	1227	<1	5.40	0.01	22.00	1085	<2	0.01	1694	188	6	88	0.07	49	<10	12
43498	<1	0.96	<10	4.6	<5	1.20	2	92	1895	<1	4.69	0.01	24.52	835	<2	0.02	1984	115	13	27	0.04	33	<10	4
43499	<1	0.27	<10	4.9	<5	0.97	2	96	2069	4	5.40	0.01	23.59	710	11	0.02	2181	44	8	47	<0.01	20	<10	<2
43501	<1	0.16	<10	5.7	<5	2.52	2	101	2497	<1	6.01	<0.01	22.24	916	<2	0.02	2159	47	7	38	<0.01	14	<10	3
43506	<1	0.12	<10	5.4	<5	0.25	2	102	1258	<1	5.68	0.01	24.43	807	<2	0.03	2252	35	8	49	<0.01	18	<10	<2
43507	<1	0.15	<10	5.2	<5	0.17	2	105	1814	<1	5.69	<0.01	24.84	769	<2	0.01	2122	25	9	3	<0.01	17	<10	<2
43508	<1	0.09	<10	5.4	<5	0.29	2	115	1249	<1	5.95	0.01	25.99	903	<2	0.01	2361	34	11	16	<0.01	17	<10	2
43509	<1	0.10	<10	5.3	<5	0.17	2	110	1052	<1	5.92	<0.01	26.84	820	<2	0.01	2298	32	11	6	<0.01	18	<10	2
43510	<1	0.06	<10	5.3	<5	0.29	3	115	852	78	6.07	0.02	26.62	910	<2	0.01	2356	20	11	8	<0.01	16	<10	13
43511	<1	0.07	<10	5.2	<5	0.09	3	117	1349	8	6.02	0.01	26.33	850	19	0.01	2358	23	14	3	<0.01	16	<10	14
43512	<1	0.10	<10	5.2	<5	0.06	3	109	1016	<1	6.10	0.01	25.99	810	<2	0.01	2232	31	6	2	<0.01	19	<10	12
43513	<1	0.10	<10	5.3	<5	0.07	3	113	2016	<1	6.23	<0.01	26.30	914	2	0.01	2346	28	8	2	<0.01	16	<10	16
43514	4	0.03	<10	4.6	<5	0.22	2	113	811	42	5.40	<0.01	26.13	826	<2	0.03	2483	31	12	4	<0.01	14	<10	14
43515	<1	0.12	<10	5.8	<5	0.90	3	124	1266	<1	6.62	0.02	27.66	922	2	0.01	2479	40	12	10	<0.01	21	<10	18
43516	<1	1.41	19	5.3	<5	2.16	2	97	1235	4	6.01	0.05	21.67	993	<2	0.03	1944	162	6	47	0.06	58	<10	34
43518	<1	0.89	<10	5.0	<5	0.88	2	105	1067	<1	5.72	0.01	24.55	1027	<2	0.01	2181	108	5	10	0.04	41	<10	24
43519	<1	0.09	<10	5.3	<5	0.32	2	117	1347	<1	6.16	<0.01	27.11	991	<2	0.01	2485	35	12	2	<0.01	18	<10	22
43520	<1	0.10	<10	4.8	<5	0.26	2	107	1212	<1	5.63	<0.01	25.50	850	<2	0.01	2275	27	9	8	<0.01	16	<10	21
43521	<1	0.12	<10	4.9	<5	0.43	2	112	1190	<1	5.78	0.01	27.93	909	<2	0.02	2314	30	6	5	<0.01	19	<10	13
43522	<1	0.25	<10	5.1	<5	0.33	2	109	1808	65	5.62	0.01	25.10	890	<2	0.02	2290	27	9	6	<0.01	23	<10	38

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2181RR

Date : Nov-19-08

Why Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
43523	<1	5.86	37	7.0	<5	1.18	1	89	1225	52	7.94	0.12	21.21	1487	<2	0.04	1331	520	<2	54	0.27	209	<10	15
43524	<1	0.18	18	5.4	<5	1.65	2	103	1421	<1	6.09	0.06	24.45	884	<2	0.01	2110	53	11	39	0.01	22	<10	20
43526	<1	0.85	198	5.7	<5	1.37	2	103	981	<1	6.16	0.35	24.38	1194	<2	0.05	2210	277	8	82	0.05	36	<10	30
43527	<1	0.10	<10	5.1	<5	0.31	3	110	1135	<1	6.08	<0.01	26.89	1039	<2	0.01	2285	30	8	15	<0.01	19	<10	22
43528	<1	0.07	<10	5.1	<5	0.48	2	123	1181	<1	6.08	<0.01	27.73	1083	<2	0.01	2617	36	10	15	<0.01	15	<10	18
43529	<1	0.21	10	5.6	<5	0.74	3	121	1491	<1	6.37	<0.01	27.10	999	<2	0.02	2539	36	4	36	0.01	20	<10	30
43530	<1	0.20	<10	5.2	<5	0.99	3	124	1109	<1	5.87	<0.01	26.73	1103	<2	0.02	2563	44	7	24	0.01	21	<10	36
43531	<1	0.12	<10	5.1	<5	0.43	2	121	1212	<1	5.96	<0.01	27.85	1001	<2	0.01	2557	35	9	12	<0.01	19	<10	36
43532	<1	0.11	<10	5.4	<5	0.46	3	114	1817	<1	6.18	<0.01	26.49	1090	<2	0.01	2409	25	7	23	<0.01	17	<10	41
43533	<1	0.12	<10	5.1	<5	0.45	2	114	1361	<1	5.93	<0.01	27.79	876	<2	0.02	2469	40	2	43	<0.01	18	<10	26
43534	<1	0.13	<10	5.5	<5	0.28	3	123	1527	<1	6.38	<0.01	28.63	1141	<2	0.01	2565	31	14	26	<0.01	18	<10	33
43535	<1	0.15	<10	5.0	<5	0.34	2	110	1323	<1	5.77	<0.01	27.12	1021	<2	0.01	2438	30	8	23	<0.01	15	<10	23
43536	<1	0.06	42	<0.5	<5	0.33	1	92	1136	3	6.16	<0.01	28.64	1070	<2	0.01	2600	50	15	26	<0.01	8	<10	35
43537	1	0.04	40	<0.5	<5	1.21	1	88	1064	4	5.79	<0.01	25.46	912	<2	0.01	2293	46	10	43	<0.01	8	<10	31
43538	<1	0.06	43	<0.5	<5	0.86	1	84	747	2	5.52	<0.01	25.44	1042	<2	0.01	2256	48	14	61	<0.01	13	<10	28
43539	1	0.09	50	<0.5	<5	0.35	1	91	998	4	5.77	0.01	25.27	914	<2	0.02	2416	50	8	33	<0.01	13	<10	31
43540	1	0.09	41	<0.5	<5	0.33	1	96	904	3	6.04	<0.01	26.07	744	<2	0.02	2510	42	13	33	<0.01	14	<10	31
43541	<1	1.02	44	<0.5	<5	2.63	1	76	1025	2	5.80	<0.01	22.95	888	<2	0.02	2106	135	7	307	0.03	30	<10	31
43542	<1	4.41	55	<0.5	<5	2.27	1	61	1131	3	6.81	0.01	19.30	1001	<2	0.08	1417	458	17	44	0.17	106	<10	57
43543	<1	0.14	54	<0.5	<5	2.23	1	76	1313	7	5.54	0.02	23.81	990	<2	0.02	2305	42	23	75	<0.01	13	<10	71
43544	<1	0.08	41	<0.5	<5	0.81	1	86	1505	2	6.03	<0.01	26.35	1015	<2	0.01	2507	43	15	34	<0.01	10	<10	55
43545	1	0.07	39	<0.5	<5	0.59	1	86	1426	3	5.66	<0.01	26.14	1138	<2	<0.01	2424	44	12	22	<0.01	7	<10	39
43546	1	0.05	40	<0.5	<5	0.38	1	80	1059	1	6.18	0.07	26.31	948	37	0.01	2370	47	15	38	<0.01	7	<10	24
43547	<1	1.44	489	<0.5	<5	1.58	2	70	1066	51	5.73	0.71	22.86	1459	<2	0.03	1868	464	192	182	0.10	39	<10	190
43548	<1	1.33	368	<0.5	<5	1.98	1	83	691	22	6.05	0.74	21.69	1256	<2	0.07	1979	452	35	178	0.09	39	<10	66
43549	1	0.11	42	<0.5	<5	1.84	1	91	898	<1	5.91	<0.01	24.77	892	<2	0.01	2310	50	9	101	<0.01	10	<10	35
43550	1	0.07	39	<0.5	<5	1.16	1	84	1067	<1	5.59	<0.01	23.74	663	<2	0.02	2230	46	16	41	<0.01	9	<10	29
43553	<1	0.69	39	<0.5	<5	3.14	1	78	929	1	5.77	0.01	21.91	975	<2	0.02	2034	80	18	74	0.02	32	<10	55
43554	1	0.10	40	<0.5	<5	0.63	1	95	1383	2	6.00	<0.01	26.51	1046	<2	0.01	2454	41	10	25	<0.01	12	<10	46
43555	<1	0.13	42	<0.5	<5	1.55	1	100	935	<1	6.34	<0.01	27.72	953	<2	0.01	2519	47	9	36	<0.01	16	<10	34

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2181RR

Date : Nov-19-08

Why Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
43556	<1	0.88	43	<0.5	<5	2.73	1	87	909	<1	5.31	0.01	24.82	930	2	0.01	2210	111	8	79	0.05	38	<10	35
43557	<1	0.15	39	<0.5	<5	4.28	1	83	929	<1	5.38	0.01	21.99	974	<2	0.02	2067	44	13	92	<0.01	16	<10	31
43561	<1	3.55	36	<0.5	<5	1.61	4	64	669	13	5.84	0.01	21.07	1603	<2	0.01	1319	415	736	48	0.21	119	<10	669
43562	1	0.10	40	<0.5	<5	1.68	1	90	1409	<1	6.56	<0.01	25.77	1053	3	0.01	2316	57	14	49	<0.01	12	<10	38
43563	1	0.05	38	<0.5	<5	0.93	1	90	922	23	5.88	<0.01	24.48	1211	<2	<0.01	2308	46	123	58	<0.01	8	<10	68
43564	1	0.04	40	<0.5	<5	0.52	1	91	1372	4	6.61	<0.01	26.50	1077	<2	<0.01	2151	42	12	33	<0.01	5	<10	32
43565	<1	0.05	<10	5.8	<5	0.49	3	112	1069	7	6.63	<0.01	25.91	1113	<2	0.01	2243	32	13	47	<0.01	12	11	19
43566	<1	0.03	<10	5.4	<5	1.33	3	116	992	1	5.98	0.01	25.99	1059	<2	0.02	2364	36	14	122	<0.01	12	<10	15
43567	<1	0.04	<10	5.2	<5	1.41	3	105	959	2	5.74	0.01	24.02	987	<2	0.01	2103	40	134	48	<0.01	14	<10	47
43570	<1	0.36	<10	5.6	<5	0.61	3	111	1487	1	6.24	0.01	27.15	1040	<2	0.02	2298	54	9	59	0.02	22	11	16
43571	<1	0.09	<10	5.1	<5	1.43	2	108	1681	2	5.80	<0.01	25.14	1115	<2	0.01	2200	39	11	112	<0.01	14	<10	18
43572	<1	1.57	<10	7.3	<5	1.18	3	153	3000	31	8.02	0.01	23.53	1015	<2	0.07	3223	129	12	35	0.06	66	10	<2
43573	<1	0.08	<10	5.2	<5	0.49	2	113	1491	3	5.79	<0.01	24.97	858	<2	0.01	2331	37	14	12	<0.01	18	<10	10
43574	<1	0.12	<10	5.2	<5	0.34	2	114	2629	1	5.87	<0.01	26.19	970	<2	0.01	2280	40	9	19	<0.01	14	<10	12
43575	<1	0.09	<10	5.2	<5	0.18	3	122	2591	6	5.94	<0.01	26.53	976	<2	0.01	2425	42	15	36	<0.01	16	<10	18
43576	<1	0.11	<10	6.0	<5	0.11	3	113	2005	1	6.84	<0.01	26.10	980	<2	0.01	2170	32	11	18	<0.01	21	<10	18
43577	<1	0.10	<10	5.8	<5	0.08	3	119	2551	4	6.54	<0.01	26.58	952	<2	0.01	2300	35	7	15	<0.01	20	<10	23
43578	<1	0.09	<10	5.0	<5	0.14	2	116	1707	2	5.66	<0.01	26.38	1030	<2	0.01	2452	29	10	23	<0.01	18	<10	16
43579	<1	0.18	<10	5.1	<5	0.36	3	112	1666	4	5.72	<0.01	25.55	1012	<2	0.01	2356	40	11	16	0.01	19	10	19
43580	<1	0.59	<10	5.1	<5	0.57	2	107	1153	6	5.81	0.01	25.94	881	<2	0.02	2263	81	12	43	0.03	32	11	17
43581	<1	0.10	<10	5.5	<5	0.25	3	118	1247	1	6.34	<0.01	27.96	1124	<2	0.01	2504	33	17	33	<0.01	20	13	17
43582	<1	0.11	<10	4.5	<5	1.11	2	101	1027	4	5.19	<0.01	23.99	1289	<2	0.01	2201	34	13	63	<0.01	17	<10	29
43583	<1	0.09	<10	5.4	<5	0.84	3	108	978	1	6.09	0.01	26.64	818	<2	0.01	2304	40	13	36	<0.01	19	<10	8
43584	<1	0.22	<10	5.4	<5	0.44	2	105	1270	1	6.03	0.01	25.04	906	<2	0.01	2334	50	10	23	<0.01	21	<10	17
43585	<1	0.08	<10	4.8	<5	0.62	2	110	975	2	5.29	0.01	24.65	933	<2	0.01	2350	31	12	9	<0.01	17	<10	10
43586	<1	1.05	<10	5.4	<5	1.29	2	103	1248	4	5.92	0.01	24.91	1221	<2	0.01	2117	137	3	22	0.03	32	<10	15
43588	<1	0.55	<10	5.2	<5	0.22	2	121	1865	127	5.55	<0.01	23.52	639	5	0.02	2188	61	11	14	0.01	20	<10	<2
43589	<1	0.12	<10	4.5	<5	0.76	2	108	1224	49	5.21	<0.01	24.82	950	<2	0.01	2209	31	14	36	<0.01	18	<10	9
43590	<1	0.13	<10	4.9	<5	0.36	2	105	961	33	5.49	<0.01	25.46	941	<2	0.01	2216	35	10	29	<0.01	19	<10	11
43591	<1	0.11	<10	4.7	<5	0.29	2	105	870	31	5.43	<0.01	24.57	850	<2	0.01	2192	36	16	30	<0.01	18	<10	23

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2181RR

Date : Nov-19-08

Why Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
43592	<1	0.14	<10	4.8	<5	0.59	2	98	1476	54	5.27	0.02	25.26	938	<2	0.02	2210	41	11	48	<0.01	20	<10	18
43593	<1	0.11	<10	5.1	<5	0.20	2	98	2082	11	5.72	0.01	26.37	934	<2	0.02	2236	39	9	8	<0.01	18	10	10
43594	5	0.05	<10	5.5	<5	0.28	13	112	973	66	6.19	0.01	26.26	1026	<2	0.02	2367	33	2108	12	<0.01	16	24	1894
43595	<1	0.09	<10	5.2	<5	0.27	2	111	1216	8	5.85	0.02	26.59	1030	<2	0.02	2256	36	22	17	<0.01	17	<10	38
43596	<1	0.06	<10	5.5	<5	0.33	2	108	931	15	6.05	0.01	26.39	1028	<2	0.02	2356	34	40	24	<0.01	15	<10	37
43597	<1	0.09	<10	5.7	<5	0.23	3	107	1473	16	6.34	0.01	25.65	1070	<2	0.02	2324	35	57	17	<0.01	17	13	86
43598	<1	0.07	<10	4.9	<5	0.34	2	89	934	19	5.30	0.01	24.04	1042	<2	0.02	2192	33	146	16	<0.01	15	<10	144
43599	<1	0.06	<10	5.0	<5	0.25	4	91	969	138	5.41	0.01	23.74	877	<2	0.02	2171	28	428	12	<0.01	14	12	486
43600	<1	1.04	<10	5.0	<5	0.41	2	98	1365	9	5.47	0.01	25.96	969	<2	0.01	1998	131	7	23	0.05	33	<10	38
43601	<1	7.10	2638	8.5	<5	6.13	1	50	441	85	6.87	3.28	7.46	2746	<2	1.34	146	3946	681	1098	0.63	190	<10	228
43602	<1	0.12	<10	5.3	<5	0.37	2	116	1856	20	5.93	0.02	27.11	1098	<2	0.02	2359	46	13	29	<0.01	15	12	21
43603	<1	0.06	<10	5.2	<5	0.14	2	113	949	42	5.88	0.01	27.07	939	<2	0.01	2475	45	11	9	<0.01	14	11	12
43604	<1	0.06	<10	5.3	<5	0.17	2	114	960	37	5.99	0.01	27.18	1043	<2	0.01	2567	40	10	16	<0.01	14	<10	14
43605	<1	0.10	<10	5.0	<5	0.21	2	108	1567	37	5.67	0.01	26.35	1102	<2	0.02	2391	36	11	53	<0.01	15	<10	19
43606	<1	0.06	<10	5.2	<5	0.15	2	113	1334	42	5.88	0.01	26.94	1093	<2	0.01	2666	39	11	31	<0.01	14	<10	19
43607	<1	0.11	<10	5.2	<5	0.63	2	108	1450	43	5.70	0.01	26.06	1106	<2	0.02	2231	35	14	45	<0.01	15	10	23
Duplicates:																								
43451	<1	4.54	854	7.4	<5	1.81	1	66	1405	12	5.09	2.16	12.68	849	<2	1.62	1362	830	13	491	0.20	64	<10	35
43460	<1	2.60	35	5.0	<5	4.36	2	75	1314	52	5.39	0.08	18.11	703	<2	0.06	1588	261	<2	75	0.14	85	10	12
43473	<1	8.27	812	4.3	<5	0.71	2	52	475	32	4.20	1.72	10.19	2720	<2	2.27	675	592	1324	214	0.22	114	11	487
43478	<1	0.10	12	5.4	<5	0.54	2	104	1089	22	6.03	0.01	24.95	718	<2	0.01	2306	30	11	32	0.01	16	<10	<2
43487	<1	0.04	<10	4.9	<5	0.41	2	136	1006	40	5.41	<0.01	27.78	834	<2	0.01	2514	27	12	6	<0.01	11	<10	<2
43501	<1	0.17	<10	6.2	<5	2.71	3	106	2334	<1	6.43	0.01	23.82	975	<2	0.02	2301	45	11	40	<0.01	15	<10	2
43510	<1	0.04	<10	5.2	<5	0.29	3	115	780	80	6.02	0.01	26.69	899	<2	0.01	2363	23	9	8	<0.01	14	<10	8
43520	<1	0.10	<10	4.9	<5	0.27	2	113	1467	<1	5.80	<0.01	26.55	886	<2	0.01	2425	31	7	8	<0.01	16	<10	16
43531	<1	0.11	<10	5.2	<5	0.44	2	122	1494	<1	6.03	0.01	28.09	1015	<2	0.02	2560	39	11	12	<0.01	16	<10	23
43536	1	0.05	43	<0.5	<5	0.33	1	90	1545	3	6.09	<0.01	28.35	1054	<2	<0.01	2614	44	17	26	<0.01	5	<10	26
43545	1	0.08	42	<0.5	<5	0.63	1	93	1420	2	6.10	<0.01	27.98	1221	<2	<0.01	2596	48	9	38	<0.01	9	<10	44
43557	<1	0.16	40	<0.5	<5	4.38	1	85	1107	1	5.55	0.01	22.74	988	<2	0.02	2098	41	7	98	<0.01	15	<10	35
43565	<1	0.04	<10	5.9	<5	0.47	3	110	964	4	6.61	<0.01	25.73	1105	<2	0.01	2229	30	8	45	<0.01	13	11	17

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2181RR

Date : Nov-19-08

Why Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
43576	<1	0.12	<10	6.2	<5	0.11	3	117	1834	5	7.04	<0.01	26.89	1015	<2	0.01	2285	32	11	19	<0.01	22	11	20
43586	<1	1.03	<10	5.5	<5	1.25	2	102	884	11	5.77	0.01	24.16	1195	<2	0.01	2082	127	9	22	0.03	34	<10	21
43592	<1	0.14	<10	4.7	<5	0.55	2	95	1206	56	5.07	<0.01	24.11	910	<2	0.01	2103	34	12	45	<0.01	20	<10	25
43601	<1	7.03	2623	8.3	<5	6.04	1	49	458	80	6.70	3.22	7.23	2685	<2	1.29	145	3914	656	1102	0.63	189	<10	217
Standards:																								
Blank	<1	0.01	<10	<0.5	<5	<0.01	<1	1	2	<1	0.02	<0.01	0.02	<5	<2	<0.01	1	<10	3	<1	<0.01	<1	<10	2
CH-4	1	7.77	488	6.0	<5	2.00	1	32	143	1988	5.77	1.88	1.45	474	<2	3.33	58	661	11	214	0.29	104	<10	214

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2217RR

Date : Nov-20-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
43608	<1	2.10	164	6.3	<5	2.05	3	99	1234	13	6.65	0.31	21.36	1176	<2	0.21	1933	442	14	160	0.16	81	11	28
43609	<1	0.18	12	5.4	<5	0.55	3	118	1088	12	6.00	0.01	23.80	848	<2	0.03	2502	50	12	30	0.01	20	<10	17
43610	<1	0.13	14	6.3	<5	0.53	3	117	1533	12	6.87	0.01	25.88	828	<2	0.03	2583	43	26	57	<0.01	20	<10	21
43611	<1	0.10	<10	5.7	<5	1.16	3	108	1541	11	6.17	0.01	24.95	866	<2	0.02	2375	44	15	44	<0.01	18	<10	20
43612	<1	0.10	<10	5.8	<5	0.63	3	116	1820	13	6.33	0.01	25.29	937	<2	0.02	2485	33	20	68	<0.01	16	<10	34
43613	<1	0.11	<10	5.7	<5	0.23	3	116	1644	7	6.20	0.01	28.31	897	<2	0.02	2356	37	12	18	<0.01	13	<10	12
43614	<1	0.12	<10	6.2	<5	0.06	3	126	1616	6	6.79	0.01	28.53	802	<2	0.02	2593	40	11	11	<0.01	17	13	8
43615	<1	0.18	<10	4.8	<5	0.03	2	92	1935	7	5.26	0.01	26.63	493	<2	0.02	1918	33	9	8	<0.01	21	<10	5
43616	<1	0.09	<10	6.2	<5	0.07	3	111	1462	9	6.73	<0.01	27.08	718	<2	0.02	2417	41	14	17	<0.01	16	<10	7
43617	<1	6.96	626	9.3	<5	2.42	3	83	627	12	9.16	1.28	15.26	4321	<2	0.44	794	2321	325	356	0.52	166	16	423
43618	<1	0.14	<10	5.7	<5	0.30	3	107	1843	7	6.17	0.01	25.45	765	<2	0.02	2343	43	28	34	<0.01	16	10	29
43619	<1	0.12	<10	6.3	<5	0.19	3	104	1420	7	6.78	0.01	25.83	802	<2	0.02	2363	44	17	20	0.01	15	12	16
43620	<1	0.10	<10	5.7	<5	0.08	3	102	2078	7	6.08	0.01	26.35	735	<2	0.02	2434	34	10	8	<0.01	14	<10	16
43621	<1	0.10	<10	5.5	<5	0.03	2	95	1365	5	5.97	0.01	26.71	773	<2	0.01	2381	35	11	8	<0.01	16	<10	13
43622	<1	0.09	<10	5.4	<5	0.08	2	100	1322	5	5.85	0.01	27.53	796	<2	0.01	2405	39	9	22	<0.01	14	12	9
43623	<1	0.13	<10	6.5	<5	0.06	3	107	2817	4	7.00	0.01	26.68	991	<2	0.01	2408	42	14	73	<0.01	14	<10	12
43624	<1	0.12	<10	5.1	<5	0.01	2	98	1697	6	5.52	0.01	25.97	812	<2	0.01	2402	36	9	16	<0.01	16	12	9
43625	<1	0.15	<10	5.7	<5	0.28	3	98	2121	4	6.09	0.01	25.90	820	<2	0.01	2173	40	13	98	<0.01	17	10	8
43626	<1	0.07	<10	5.8	<5	0.56	3	108	1625	2	6.26	0.01	26.27	952	<2	0.01	2363	41	11	58	<0.01	16	<10	7
43627	<1	1.60	<10	5.7	<5	0.74	2	103	943	3	6.15	0.01	24.62	960	<2	0.01	2031	191	9	36	0.08	59	10	7
43628	<1	0.54	<10	5.9	<5	1.00	3	108	1147	3	6.45	0.01	26.12	1003	<2	0.01	2214	94	7	50	0.03	27	<10	8
43629	<1	0.05	<10	5.7	<5	0.38	3	113	1062	6	6.25	0.01	27.35	932	<2	0.01	2452	40	10	47	<0.01	12	11	5
43630	<1	0.02	<10	5.7	<5	0.15	3	116	790	5	6.21	0.01	27.76	886	<2	0.01	2478	39	12	23	<0.01	11	<10	<2
43631	<1	0.08	<10	5.6	<5	0.35	3	111	1098	4	6.13	0.01	27.04	895	<2	0.01	2371	38	8	48	<0.01	15	<10	7
43632	<1	0.09	<10	5.7	<5	0.71	3	108	1085	3	6.12	0.01	25.84	897	<2	0.01	2284	33	8	40	<0.01	16	10	50
43633	<1	2.73	308	5.6	<5	1.09	2	92	851	<1	5.86	0.84	21.11	852	<2	0.04	1761	366	10	268	0.07	52	<10	32
43634	<1	0.02	<10	5.6	<5	0.66	2	114	903	<1	5.93	<0.01	24.03	887	<2	0.01	2228	36	10	24	<0.01	12	<10	6
43635	<1	0.11	<10	4.7	<5	1.39	2	118	1494	2	5.12	0.01	25.12	874	<2	0.01	2315	35	5	62	<0.01	15	<10	6
43636	<1	0.05	<10	5.8	<5	0.16	2	127	1340	<1	6.28	<0.01	24.97	851	<2	0.01	2461	31	10	12	<0.01	12	<10	3
43637	<1	0.10	<10	5.3	<5	0.26	2	136	2283	<1	5.82	<0.01	25.73	991	<2	0.01	2394	40	7	20	<0.01	12	<10	8

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2217RR

Date : Nov-20-08

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
43638	<1	0.12	<10	5.7	<5	0.34	2	113	1527	8	6.16	0.01	26.10	809	<2	0.02	2327	39	7	24	<0.01	15	<10	6
43639	<1	7.51	1681	7.3	<5	3.94	1	36	218	58	5.59	3.11	6.05	1049	<2	2.02	95	2618	3	778	0.55	172	<10	64
43640	<1	0.15	16	5.7	<5	0.41	2	102	1303	<1	6.00	0.04	25.52	672	<2	0.03	2371	61	7	38	0.01	16	10	14
43641	<1	0.13	19	5.3	<5	0.12	2	102	863	<1	5.74	0.04	26.94	667	<2	0.03	2387	57	9	17	0.01	17	<10	61
43642	<1	0.08	<10	5.3	<5	0.18	2	98	1038	<1	5.76	<0.01	26.69	730	<2	0.01	2363	29	9	13	<0.01	16	<10	10
43643	<1	0.08	<10	5.3	<5	0.11	2	101	1103	<1	5.87	0.01	26.19	779	<2	0.01	2306	39	9	8	<0.01	15	<10	13
43644	<1	0.05	<10	5.3	<5	0.24	2	111	1220	<1	5.92	<0.01	26.62	907	<2	0.01	2358	32	6	13	<0.01	14	<10	13
43645	<1	0.06	<10	5.2	<5	1.41	2	114	930	<1	5.62	0.01	25.43	970	<2	0.01	2403	32	14	87	<0.01	14	<10	17
43646	<1	0.12	<10	5.0	<5	3.93	3	89	1512	<1	5.13	<0.01	20.37	981	<2	0.02	1897	36	616	386	<0.01	17	<10	230
43655	<1	1.07	<10	5.9	<5	3.82	4	84	1341	7	5.24	<0.01	18.73	2466	<2	0.03	1757	173	161	285	0.04	38	<10	429
43656	<1	1.53	<10	5.2	<5	4.56	3	86	1067	19	5.39	<0.01	19.45	1388	<2	0.01	1597	161	95	693	0.08	56	<10	188
43657	<1	0.94	56	6.8	<5	4.92	2	109	1276	<1	6.21	0.06	19.47	1464	<2	0.02	2029	515	80	790	0.08	42	10	84
43658	15	8.62	1346	12.7	<5	2.43	73	78	655	169	11.58	1.02	11.96	7087	<2	0.31	251	5223	1673	369	0.82	233	120	>10000
43659	8	0.07	<10	5.1	<5	0.62	4	103	1037	17	5.55	0.01	23.58	1221	<2	0.02	2120	40	235	163	<0.01	14	11	545
43660	<1	0.22	13	5.5	<5	0.73	5	103	1091	5	5.93	0.01	23.31	1391	<2	0.02	2076	84	152	54	0.01	19	12	697
43661	<1	0.06	<10	4.9	<5	0.38	2	108	909	<1	5.55	<0.01	25.00	886	<2	0.01	2146	39	13	54	<0.01	15	10	107
43662	<1	0.08	<10	4.9	<5	0.28	2	98	744	<1	4.96	0.01	23.35	856	<2	0.01	2009	29	17	77	<0.01	14	<10	102
43663	<1	0.10	<10	5.0	<5	0.23	2	104	975	<1	5.42	<0.01	24.17	823	<2	0.02	2119	31	9	30	<0.01	18	<10	72
43664	2	0.07	<10	5.4	<5	0.32	3	115	1183	17	5.95	0.01	26.53	847	<2	0.02	2385	44	10	20	<0.01	15	10	8
43665	<1	0.07	<10	5.8	<5	0.46	3	126	1304	15	6.61	0.01	28.90	1068	<2	0.01	2686	42	12	60	<0.01	16	<10	16
43666	<1	0.23	<10	3.6	<5	6.09	2	76	758	13	4.09	<0.01	23.78	1148	<2	0.01	1395	75	11	295	0.01	18	<10	4
43667	<1	0.09	<10	5.9	<5	0.23	3	116	1634	11	6.51	<0.01	27.83	917	<2	0.01	2463	37	11	23	<0.01	18	11	<2
43668	<1	0.07	<10	5.8	<5	0.13	3	124	1088	16	6.52	<0.01	27.91	973	<2	0.01	2538	33	10	13	<0.01	19	11	3
43669	<1	0.11	<10	5.3	<5	0.66	2	115	1564	9	5.83	<0.01	27.06	1215	<2	<0.01	2410	34	13	91	<0.01	19	<10	26
43670	<1	0.12	<10	4.7	<5	1.10	2	108	1148	19	5.23	<0.01	26.12	987	<2	0.01	2286	33	11	102	<0.01	20	11	13
43671	<1	0.12	<10	5.1	<5	0.36	2	115	1210	10	5.61	<0.01	26.90	818	<2	0.01	2451	35	11	31	<0.01	23	10	<2
43672	<1	0.10	<10	5.2	<5	0.59	2	114	876	14	5.71	<0.01	26.30	923	<2	0.01	2345	29	10	49	<0.01	21	<10	28
43673	<1	0.11	<10	5.9	<5	0.57	3	123	1110	12	6.43	<0.01	27.24	944	<2	0.01	2513	37	10	99	<0.01	25	<10	<2
43674	<1	0.13	<10	5.9	<5	0.63	3	117	1320	5	6.49	<0.01	27.81	870	13	0.02	2289	29	12	24	<0.01	27	<10	<2
43675	<1	1.60	<10	7.1	<5	3.59	3	120	2184	14	7.72	0.01	27.88	1887	<2	0.01	2356	296	11	201	0.10	60	<10	9

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2217RR

Date : Nov-20-08

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
43678	<1	0.24	<10	6.0	<5	0.55	2	118	1361	14	6.22	<0.01	26.25	1159	<2	0.01	2387	44	10	14	0.01	29	10	<2
43679	<1	0.10	<10	5.5	<5	1.01	2	113	1189	12	5.75	<0.01	26.42	985	<2	0.01	2326	38	10	26	<0.01	21	<10	<2
43680	<1	0.07	<10	5.2	<5	0.99	2	108	964	13	5.60	<0.01	27.59	847	<2	0.02	2249	30	8	19	<0.01	19	10	<2
43681	<1	0.11	<10	5.5	<5	0.90	2	111	1483	13	5.92	<0.01	27.79	679	<2	0.02	2317	31	11	17	<0.01	26	<10	<2
43682	<1	0.07	<10	5.0	<5	0.46	2	104	960	11	5.55	<0.01	26.79	590	<2	0.02	2236	29	9	11	<0.01	22	<10	<2
43683	<1	0.13	<10	5.2	<5	0.50	2	99	1419	8	5.59	<0.01	27.53	581	<2	0.02	2075	25	10	11	<0.01	23	10	<2
43684	<1	0.06	<10	5.7	<5	0.75	3	123	1070	11	6.19	<0.01	26.53	800	<2	0.01	2523	31	9	13	<0.01	20	<10	<2
43685	<1	0.11	<10	5.7	<5	0.48	3	117	1248	14	6.28	<0.01	26.88	716	<2	0.01	2497	37	9	9	<0.01	21	<10	<2
43686	<1	0.09	<10	5.1	<5	0.65	2	108	903	8	5.60	<0.01	25.96	645	<2	0.01	2341	30	9	14	<0.01	19	<10	<2
43687	<1	0.40	<10	5.1	<5	0.76	2	104	1275	10	5.53	<0.01	25.74	975	<2	0.01	2301	67	9	16	0.01	22	<10	<2
43688	<1	1.76	<10	6.0	<5	0.37	2	118	1334	29	6.41	<0.01	25.74	861	<2	0.01	2321	195	11	17	0.05	42	<10	<2
43689	<1	7.28	<10	5.3	<5	0.63	1	62	793	12	5.76	0.01	21.47	1598	<2	0.16	1023	844	<2	54	0.20	115	11	8
43690	<1	0.06	<10	5.7	<5	0.80	3	112	981	<1	6.04	<0.01	25.02	831	<2	0.01	2361	37	8	53	<0.01	18	<10	4
43691	<1	0.24	<10	5.9	<5	0.64	3	98	1122	2	6.08	0.01	25.12	781	<2	0.01	2301	44	10	40	0.01	22	<10	10
43692	<1	0.57	<10	4.0	<5	0.09	2	86	952	3	4.26	<0.01	19.56	325	<2	0.02	1847	27	10	11	<0.01	40	<10	11
43693	<1	0.38	<10	4.4	<5	0.05	2	90	848	17	4.68	<0.01	19.68	320	<2	0.02	1893	35	12	11	<0.01	33	<10	11
43694	<1	0.30	<10	4.1	<5	0.16	2	85	733	20	4.43	<0.01	19.01	354	<2	0.02	1770	28	13	14	<0.01	26	<10	11
43695	<1	0.18	<10	6.1	<5	0.77	3	124	1410	52	6.23	<0.01	25.21	1076	<2	0.01	2532	38	12	58	<0.01	20	<10	30
43696	<1	0.11	<10	5.6	<5	1.24	2	114	1609	20	5.71	0.01	25.34	1113	<2	0.01	2369	37	10	154	<0.01	19	<10	23
43697	<1	0.08	<10	4.5	<5	2.08	2	88	1316	13	4.67	0.01	25.25	1205	<2	0.01	1857	39	11	307	<0.01	13	<10	21
43698	<1	0.11	<10	5.2	<5	1.15	2	95	1728	4	5.35	<0.01	24.73	1171	<2	0.01	2021	31	10	128	<0.01	14	<10	10
43699	<1	0.12	<10	5.0	<5	0.96	2	87	1407	<1	4.62	<0.01	22.92	1001	<2	<0.01	1916	29	6	114	<0.01	18	<10	7
43700	<1	0.29	<10	5.2	<5	2.91	2	82	1588	3	4.55	0.01	24.56	1343	<2	0.01	1824	43	13	440	0.01	24	<10	13
43701	<1	0.47	<10	5.2	<5	4.01	2	93	1555	30	5.15	0.01	19.88	1211	<2	0.02	1831	67	29	378	0.02	23	<10	75
43702	<1	0.87	<10	5.0	<5	3.61	2	94	1372	2	5.18	0.01	19.10	925	<2	0.03	1949	75	10	175	0.03	37	<10	12
43703	<1	2.03	104	4.9	<5	2.93	2	96	1324	1	4.75	0.18	17.45	857	<2	0.09	1827	309	12	164	0.08	62	<10	20
Duplicates:																								
43608	<1	2.05	161	6.2	<5	2.00	2	98	1305	6	6.45	0.30	20.88	1142	<2	0.20	1938	424	14	157	0.15	80	<10	19
43617	<1	6.81	626	9.2	<5	2.38	3	83	680	13	9.01	1.27	14.94	4243	<2	0.36	799	2314	305	352	0.51	165	18	428
43627	<1	1.64	<10	6.0	<5	0.76	2	105	1011	4	6.36	0.01	25.00	988	<2	0.02	2077	192	10	38	0.09	62	<10	17

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2217RR

Date : Nov-20-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
43632	<1	0.09	<10	5.5	<5	0.70	2	108	1112	<1	6.06	<0.01	25.57	895	<2	0.01	2262	32	11	38	<0.01	17	<10	52
43641	<1	0.13	18	5.0	<5	0.12	2	99	828	<1	5.51	0.03	25.72	647	<2	0.03	2341	60	9	18	0.01	17	<10	66
43659	5	0.07	<10	5.1	<5	0.60	4	103	850	18	5.44	<0.01	23.10	1192	<2	0.02	2083	36	213	162	<0.01	15	10	547
43664	<1	0.08	<10	5.5	<5	0.34	2	116	1388	16	6.13	<0.01	27.48	880	<2	0.01	2441	23	10	21	<0.01	15	<10	<2
43673	<1	0.11	<10	5.9	<5	0.58	3	123	1322	12	6.54	<0.01	27.71	958	<2	0.01	2523	38	11	104	<0.01	24	<10	<2
43685	<1	0.11	<10	5.8	<5	0.48	2	116	1277	11	6.28	<0.01	26.90	716	<2	0.01	2457	29	11	9	<0.01	21	<10	<2
43690	<1	0.06	<10	5.6	<5	0.78	2	110	998	<1	5.97	<0.01	24.66	821	<2	0.01	2283	30	12	49	<0.01	18	<10	7
43699	<1	0.13	<10	5.5	<5	1.05	2	95	1501	3	5.07	<0.01	25.18	1093	<2	<0.01	2100	35	8	124	<0.01	20	<10	9
Standards:																								
Blank	<1	<0.01	<10	<0.5	<5	<0.01	<1	1	<1	3	0.01	0.01	0.01	<5	<2	<0.01	<1	<10	<2	<1	<0.01	<1	<10	6
CH-4	2	7.85	482	5.9	<5	2.01	2	33	110	2022	5.52	1.85	1.52	473	<2	3.30	50	647	13	211	0.30	103	10	215

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2246RR

Date : Nov-20-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
43706	<1	1.56	163	4.8	<5	2.05	2	76	1308	34	4.61	0.43	18.72	636	<2	0.32	1674	294	21	150	0.07	32	<10	29
43707	<1	0.10	<10	5.3	<5	2.97	3	106	1403	6	5.82	0.02	25.23	1061	<2	0.02	2312	41	14	68	<0.01	16	11	21
43708	<1	0.09	<10	5.9	<5	1.44	3	106	1628	3	6.54	0.01	26.80	928	<2	0.01	2267	41	9	32	<0.01	18	10	26
43709	<1	0.04	<10	5.0	<5	0.56	2	117	882	4	5.64	0.01	27.89	827	<2	0.01	2671	33	11	15	<0.01	14	<10	15
43710	<1	0.12	<10	5.7	<5	0.39	3	123	1556	3	6.36	0.01	27.21	688	<2	0.01	2478	31	12	15	<0.01	18	<10	13
43711	<1	0.11	<10	5.9	<5	0.11	3	111	1853	3	6.19	0.02	28.27	795	<2	0.01	2499	36	9	11	<0.01	17	<10	11
43712	<1	0.06	<10	5.4	<5	0.41	3	117	1570	2	6.04	<0.01	28.25	819	<2	<0.01	2432	39	10	18	<0.01	15	<10	9
43713	<1	0.06	<10	5.3	<5	0.75	2	110	2388	6	5.90	<0.01	27.72	939	<2	<0.01	2358	39	10	21	<0.01	11	<10	8
43714	<1	0.07	<10	4.8	<5	0.55	2	112	1542	4	5.36	<0.01	26.99	850	<2	<0.01	2447	39	11	14	<0.01	13	<10	8
43715	<1	0.09	<10	5.4	<5	0.91	3	110	1238	<1	5.96	0.01	26.57	836	<2	0.01	2423	39	10	16	<0.01	16	<10	10
43716	<1	0.32	<10	5.4	<5	0.32	2	117	1489	4	6.16	0.01	26.35	736	<2	0.01	2549	55	11	11	0.01	23	13	10
43717	<1	2.25	<10	5.7	<5	0.43	2	85	1385	4	6.30	0.01	25.24	619	<2	0.01	1740	218	9	18	0.10	64	<10	3
43718	<1	0.46	<10	5.3	<5	0.56	2	106	1541	<1	5.93	<0.01	27.00	860	<2	<0.01	2276	62	10	12	0.02	25	<10	7
43719	<1	0.16	<10	4.6	<5	0.76	2	101	1420	<1	5.30	<0.01	27.71	808	<2	<0.01	2346	38	8	11	<0.01	18	<10	8
43720	<1	0.12	<10	5.6	<5	0.23	2	116	1480	1	6.33	<0.01	28.44	915	<2	<0.01	2592	34	13	6	<0.01	17	11	8
43721	<1	0.08	<10	5.5	<5	0.24	3	119	1140	<1	6.24	<0.01	28.31	1042	<2	<0.01	2540	25	8	21	<0.01	15	12	5
43722	<1	0.10	<10	5.6	<5	0.10	2	121	1561	<1	6.36	<0.01	29.24	1048	<2	<0.01	2573	28	14	39	<0.01	16	11	7
43723	<1	0.13	<10	5.4	<5	0.10	2	117	1612	2	6.21	<0.01	28.44	1039	<2	<0.01	2517	31	8	38	<0.01	17	12	6
43724	<1	0.05	<10	5.3	<5	0.24	2	117	1288	3	6.06	<0.01	27.72	1150	<2	<0.01	2568	32	14	19	<0.01	13	<10	9
43725	<1	0.02	<10	5.8	<5	0.29	3	127	1357	4	6.65	<0.01	28.16	1163	<2	<0.01	2502	29	10	15	<0.01	10	<10	9
43726	<1	0.03	<10	5.1	<5	1.38	2	117	999	5	5.82	<0.01	26.27	1039	<2	<0.01	2399	36	7	30	<0.01	11	<10	9
43727	<1	0.41	<10	4.8	<5	6.81	2	100	1301	6	5.41	<0.01	20.40	1176	<2	<0.01	2091	65	5	79	0.01	24	<10	6
43728	<1	9.68	423	6.2	<5	2.62	1	40	92	81	6.35	2.08	4.75	985	<2	3.98	90	1107	3	440	0.32	192	<10	32
43729	<1	9.78	531	7.5	<5	4.51	1	46	71	13	7.68	3.04	4.31	1286	<2	2.51	50	895	<2	560	0.49	332	<10	37
43730	<1	10.24	485	0.9	<5	5.22	2	36	36	9	8.03	2.66	5.46	1270	2	2.41	49	1057	12	478	0.49	316	<10	50
43731	<1	0.40	49	<0.5	<5	2.04	1	85	1212	10	5.93	0.03	21.78	688	<2	0.05	2237	63	21	88	0.01	15	<10	24
43732	<1	0.18	46	<0.5	<5	1.60	1	99	1515	3	6.50	0.04	26.44	1027	<2	0.05	2379	61	13	39	0.01	9	<10	33
43733	<1	0.05	46	<0.5	<5	0.54	1	101	1298	<1	6.44	0.01	29.73	1111	<2	0.02	2635	50	25	37	<0.01	6	<10	37
43734	<1	0.05	46	<0.5	<5	0.43	1	100	1409	<1	6.47	0.01	30.49	1100	<2	0.02	2561	44	29	25	<0.01	7	<10	38
43735	<1	0.08	45	<0.5	<5	0.16	1	102	2404	<1	6.89	0.01	29.65	1022	<2	0.02	2537	51	20	23	<0.01	7	<10	47

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2246RR

Date : Nov-20-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
43736	<1	0.08	44	<0.5	<5	0.13	1	107	2724	<1	7.15	0.01	29.29	976	<2	0.02	2634	55	25	15	<0.01	9	<10	41
43737	<1	0.10	44	<0.5	<5	0.21	1	102	1826	<1	6.64	0.01	28.84	909	<2	0.02	2557	47	11	20	<0.01	11	<10	29
43738	1	0.10	46	<0.5	<5	0.13	1	102	1694	<1	6.52	0.01	30.25	1058	<2	0.02	2598	50	13	72	<0.01	13	<10	28
43739	1	0.11	46	<0.5	<5	0.14	1	107	1758	<1	6.91	0.01	29.76	965	<2	0.02	2763	51	35	66	<0.01	13	<10	28
43740	<1	0.14	45	<0.5	<5	0.03	1	96	2081	<1	6.46	0.01	30.06	913	<2	0.02	2631	48	21	22	<0.01	14	<10	28
43741	<1	0.11	45	<0.5	<5	0.04	1	111	2051	2	7.24	0.01	30.40	982	<2	0.02	2803	54	16	31	<0.01	13	<10	28
43742	<1	0.09	44	<0.5	<5	0.03	1	106	1802	<1	7.24	<0.01	30.64	1009	<2	0.01	2649	49	14	15	<0.01	12	<10	27
43743	<1	0.07	44	<0.5	<5	0.14	1	105	1511	3	6.97	0.01	30.54	1007	<2	0.02	2662	53	22	43	<0.01	12	<10	28
43744	1	0.10	44	<0.5	<5	0.23	1	103	1726	2	6.55	0.01	29.49	1077	<2	0.02	2702	45	16	44	<0.01	13	<10	31
43745	<1	0.12	45	<0.5	<5	0.25	1	106	1439	1	6.26	0.01	30.62	967	<2	0.02	2657	48	14	46	<0.01	14	<10	29
43746	<1	0.08	45	<0.5	<5	0.15	1	113	1512	2	7.13	<0.01	30.84	1165	<2	0.02	2909	55	14	26	<0.01	11	<10	25
43747	1	1.37	44	<0.5	<5	0.31	1	90	1002	<1	6.46	0.01	28.44	1176	<2	0.02	2185	178	22	41	0.08	44	<10	22
43748	<1	0.08	44	<0.5	<5	0.18	1	107	1525	3	6.43	<0.01	28.79	1127	<2	0.03	2711	45	13	20	<0.01	13	<10	25
43749	<1	0.05	44	<0.5	<5	0.15	1	106	1373	3	6.73	<0.01	29.63	1273	<2	0.01	2576	49	16	16	<0.01	9	<10	24
43750	1	0.07	44	<0.5	<5	0.08	1	115	1553	7	6.57	<0.01	30.47	1225	<2	0.01	2712	46	21	19	<0.01	10	<10	29
43751	<1	0.16	42	<0.5	<5	0.25	1	108	2001	2	6.20	<0.01	27.90	922	<2	0.02	2309	47	13	23	<0.01	14	<10	32
43752	<1	0.18	43	<0.5	<5	0.62	<1	110	1930	5	6.10	0.01	27.88	832	10	0.03	2543	49	29	34	<0.01	15	<10	35
43753	<1	0.07	55	<0.5	<5	0.11	1	117	1498	5	6.56	<0.01	29.53	1132	<2	0.02	2697	49	33	24	<0.01	9	<10	32
43754	<1	0.12	45	<0.5	<5	0.12	1	105	1787	21	6.33	0.01	28.55	906	5	0.02	2570	56	82	33	<0.01	12	<10	94
43755	<1	0.09	40	<0.5	<5	1.21	4	79	1852	21	5.31	0.01	23.58	1408	<2	0.02	2222	43	243	68	<0.01	10	<10	732
43756	<1	0.11	53	<0.5	<5	1.07	1	103	2548	4	6.04	0.01	26.99	949	2	0.02	2482	53	169	70	<0.01	11	<10	229
43757	1	0.12	42	<0.5	<5	1.32	<1	94	2012	<1	5.87	0.01	26.79	835	<2	0.02	2423	51	20	104	<0.01	12	<10	46
43758	<1	0.09	48	<0.5	<5	0.57	1	101	1997	<1	6.75	0.01	27.36	874	6	0.02	2497	54	15	65	<0.01	10	<10	36
43759	<1	0.08	40	<0.5	<5	0.09	1	94	1334	<1	5.97	<0.01	27.19	614	<2	0.01	2498	45	16	16	<0.01	11	<10	28
43760	<1	0.07	41	<0.5	<5	0.48	<1	81	1490	<1	4.93	0.01	26.09	1001	2	0.01	2276	43	26	39	<0.01	8	<10	46
43761	<1	0.12	41	<0.5	<5	0.89	<1	73	1937	<1	5.59	0.01	26.21	820	2	0.01	2240	42	29	62	<0.01	13	<10	43
43762	<1	0.10	41	<0.5	<5	0.13	1	86	1274	<1	5.92	0.01	26.60	853	<2	0.02	2292	47	29	21	<0.01	12	<10	37
43763	<1	0.09	40	<0.5	<5	0.08	1	88	1362	<1	6.26	<0.01	27.07	787	<2	0.01	2350	49	16	18	<0.01	12	<10	30
43764	<1	0.17	42	<0.5	<5	0.66	1	91	1564	<1	6.54	0.01	26.97	889	<2	0.02	2381	54	21	82	0.01	17	<10	35
43765	<1	0.11	41	<0.5	<5	1.58	1	96	1298	<1	6.29	0.01	26.24	978	<2	0.02	2429	49	26	119	<0.01	13	<10	32

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2246RR

Date : Nov-20-08

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
43766	<1	0.09	39	<0.5	<5	0.70	1	82	1182	<1	6.27	<0.01	24.84	821	<2	0.01	2326	44	21	24	<0.01	12	<10	47
43767	<1	0.41	38	<0.5	<5	3.38	1	88	1447	<1	6.51	0.01	24.52	1073	<2	0.02	2356	76	19	68	0.02	18	<10	32
43768	<1	3.99	134	<0.5	<5	4.01	7	55	1122	30	6.80	0.39	16.69	2111	8	0.22	1463	465	286	180	0.16	96	<10	1010
43769	<1	10.79	625	0.6	<5	0.85	<1	49	481	<1	6.25	1.58	14.62	2691	30	1.10	545	1299	8	299	0.29	184	<10	224
43770	<1	0.17	40	<0.5	<5	0.71	<1	74	1698	<1	5.35	0.01	24.42	667	<2	0.02	2090	47	19	150	<0.01	13	<10	34
43771	1	1.93	49	<0.5	<5	0.63	<1	66	1578	<1	5.33	0.03	24.36	1066	4	0.03	2046	245	18	42	0.05	34	<10	45
43772	1	0.11	41	<0.5	<5	0.65	1	95	1382	140	5.81	0.01	27.17	842	2	0.01	2428	46	25	39	<0.01	11	<10	28
43773	1	0.12	40	<0.5	<5	1.43	1	91	1196	<1	5.88	<0.01	26.73	875	<2	0.01	2451	50	15	50	<0.01	12	<10	21
43774	1	0.10	40	<0.5	<5	0.95	1	89	1296	176	6.04	0.01	24.89	1217	<2	0.02	2265	47	47	47	<0.01	12	<10	75
43775	1	0.15	40	<0.5	<5	0.68	1	93	1737	52	6.36	0.01	25.48	1306	<2	0.02	2235	51	57	67	<0.01	12	<10	94
43776	<1	0.12	41	<0.5	<5	1.02	<1	86	2436	<1	5.68	0.01	26.55	1266	<2	0.02	2480	48	32	89	<0.01	11	<10	65
43777	1	0.08	42	<0.5	<5	0.69	1	87	1948	33	6.20	<0.01	27.96	1159	<2	0.01	2266	43	37	52	<0.01	10	<10	125
43778	5	0.12	33	<0.5	<5	0.81	4	87	1599	925	5.81	0.01	23.52	1215	<2	0.02	2116	56	172	40	<0.01	8	<10	587
43779	<1	0.12	34	<0.5	<5	0.76	<1	98	1680	4	5.62	0.01	27.46	1107	<2	0.02	2461	39	15	49	<0.01	10	<10	41
43780	3	1.02	34	<0.5	<5	0.93	1	101	1922	301	6.63	0.01	24.67	1425	4	0.02	2121	159	42	64	0.07	43	<10	137
43781	<1	0.08	34	<0.5	<5	0.26	<1	107	1953	5	6.43	0.01	27.15	1171	<2	0.02	2467	42	18	13	<0.01	5	<10	47
43782	<1	0.04	35	<0.5	<5	0.25	1	109	1125	2	6.30	<0.01	27.80	1115	<2	0.02	2570	40	15	16	<0.01	5	<10	35
43783	<1	0.03	33	<0.5	<5	0.33	1	111	1139	2	6.80	<0.01	27.05	986	<2	0.01	2535	45	13	10	<0.01	4	<10	75
43784	1	0.02	35	<0.5	<5	0.44	1	112	1034	4	6.49	<0.01	27.51	1062	<2	0.03	2565	41	11	12	<0.01	4	<10	32
43785	<1	0.04	35	<0.5	<5	1.15	1	97	1254	8	7.32	<0.01	27.40	1252	<2	0.03	2521	53	16	50	<0.01	5	<10	44
43786	<1	0.09	36	<0.5	<5	0.09	<1	115	1518	2	5.88	<0.01	28.48	1182	<2	0.02	2534	41	20	9	<0.01	6	<10	57
43787	<1	0.07	36	<0.5	<5	0.27	<1	107	1577	2	6.49	0.01	26.49	1082	<2	0.02	2477	47	14	16	<0.01	7	<10	41
43788	<1	0.07	35	<0.5	<5	0.14	<1	106	1774	2	6.59	<0.01	26.73	1123	<2	0.02	2451	45	15	9	<0.01	6	<10	40
43789	<1	0.10	34	<0.5	<5	0.10	<1	106	2383	2	5.78	<0.01	27.17	1214	<2	0.02	2526	41	29	15	<0.01	3	<10	50
43790	<1	0.09	36	<0.5	<5	0.44	<1	95	1395	4	5.79	<0.01	26.17	1083	<2	0.02	2268	39	117	45	<0.01	8	<10	46
43791	<1	0.10	35	<0.5	<5	0.18	1	102	1365	3	6.30	<0.01	27.90	994	<2	0.02	2512	43	15	34	<0.01	9	<10	32
43792	<1	0.10	36	<0.5	<5	0.16	1	96	1068	7	6.27	<0.01	27.63	1002	<2	0.02	2517	39	23	29	<0.01	8	<10	44
43793	<1	0.09	34	<0.5	<5	0.03	<1	93	1137	2	5.77	<0.01	27.27	860	<2	0.01	2439	41	13	<1	<0.01	8	<10	26
43794	<1	0.07	34	<0.5	<5	0.10	1	100	1266	3	6.11	<0.01	26.88	993	<2	0.01	2466	34	21	27	<0.01	6	<10	29
43795	1	0.06	38	<0.5	<5	0.16	<1	101	1507	3	6.47	<0.01	27.00	1063	<2	0.01	2456	44	51	32	<0.01	4	<10	29

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2246RR

Date : Nov-20-08

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
43796	<1	0.03	34	<0.5	<5	0.15	1	97	1354	2	5.96	<0.01	26.56	969	<2	0.02	2391	38	98	24	<0.01	3	<10	151
43797	<1	0.03	43	<0.5	<5	0.13	<1	104	1095	4	6.34	<0.01	27.37	951	<2	0.01	2455	43	14	20	<0.01	4	<10	33
43798	1	0.02	36	<0.5	<5	0.46	1	94	995	5	5.48	<0.01	25.38	1237	<2	0.01	2236	36	168	79	<0.01	4	<10	86
43799	<1	0.59	42	<0.5	<5	1.44	1	84	1001	15	5.85	0.01	23.63	1403	<2	0.02	2061	349	161	188	0.05	19	<10	178
43800	1	0.14	48	<0.5	<5	1.41	3	92	1167	18	5.91	0.01	23.97	1323	<2	0.02	2313	52	604	223	0.01	7	<10	746
Duplicates:																								
43706	<1	1.31	142	3.9	<5	1.72	2	64	905	30	3.90	0.35	18.69	537	<2	0.27	1653	247	16	132	0.06	29	<10	23
43715	<1	0.10	<10	5.5	<5	0.96	3	115	1511	3	6.28	0.01	27.12	881	<2	0.02	2490	43	13	18	0.01	17	10	6
43725	<1	0.02	<10	5.6	<5	0.29	3	125	1368	6	6.56	<0.01	27.39	1147	<2	0.01	2463	33	10	15	<0.01	10	11	8
43730	<1	9.70	458	0.8	<5	4.88	1	34	40	9	7.38	2.54	5.25	1198	<2	2.31	52	991	15	442	0.46	297	<10	45
43739	1	0.11	47	<0.5	<5	0.14	1	112	1750	<1	7.17	0.01	31.09	996	<2	0.02	2856	56	22	72	<0.01	13	<10	25
43749	<1	0.06	45	<0.5	<5	0.15	1	107	1481	3	6.83	0.01	29.58	1273	<2	0.01	2604	50	19	17	<0.01	9	<10	42
43754	1	0.11	41	<0.5	<5	0.11	1	100	1647	<1	6.10	0.01	27.61	869	3	0.02	2462	45	72	20	<0.01	11	<10	88
43763	1	0.09	40	<0.5	<5	0.08	1	91	1503	<1	6.47	0.01	27.65	804	<2	0.02	2423	58	21	20	<0.01	13	<10	32
43773	<1	0.12	43	<0.5	<5	1.51	1	97	1241	<1	6.38	0.01	28.04	905	<2	0.01	2514	51	20	59	<0.01	12	<10	23
43778	4	0.12	35	<0.5	<5	0.86	4	92	1653	971	6.25	0.01	24.96	1287	<2	0.02	2202	49	183	47	<0.01	9	<10	626
43787	<1	0.08	37	<0.5	<5	0.28	1	110	1631	3	6.75	0.01	27.65	1130	<2	0.02	2558	46	19	21	<0.01	8	<10	41
43797	<1	0.02	44	<0.5	<5	0.13	1	101	855	4	6.22	<0.01	27.14	929	<2	0.01	2399	44	18	22	<0.01	4	<10	31
Standards:																								
BLANK	<1	0.01	<10	<0.5	<5	<0.01	<1	1	2	<1	0.01	<0.01	0.01	<5	<2	0.01	1	<10	<2	<1	<0.01	<1	<10	<2
CH-4	2	7.70	483	0.9	<5	1.99	2	29	135	1971	5.47	1.78	1.42	473	2	3.27	64	721	15	209	0.30	98	<10	221

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2333RR

Date : Jul-11-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
43803	<1	0.06	30	5.3	<5	1.19	2	104	759	9	4.77	0.01	21.37	829	<2	0.01	2178	28	17	333	<0.01	11	<10	29
43804	<1	0.06	17	4.9	<5	0.99	1	91	733	4	4.52	0.01	21.39	949	<2	0.01	1910	26	20	241	<0.01	11	<10	25
43805	1	0.68	42	5.5	<5	1.47	11	78	1154	124	4.86	0.01	18.18	1461	<2	0.02	1547	332	1814	210	0.05	28	<10	1974
43806	<1	0.11	10	5.1	<5	1.15	1	91	1173	23	4.61	0.01	19.69	986	<2	0.02	1878	17	19	170	<0.01	14	<10	53
43807	<1	0.10	<10	5.5	<5	0.42	2	91	1487	24	5.32	0.01	22.92	1072	<2	0.01	2021	22	29	49	<0.01	13	<10	50
43808	<1	0.12	<10	5.4	<5	0.57	2	95	1224	12	5.11	<0.01	22.57	954	<2	0.02	1999	27	89	54	0.01	15	<10	105
43809	<1	0.09	16	5.5	<5	0.23	2	106	1154	1	5.34	<0.01	24.32	734	<2	0.02	2234	19	19	106	<0.01	15	<10	21
43810	<1	0.10	18	6.2	<5	0.58	3	104	1285	<1	5.84	<0.01	23.79	827	<2	0.02	2131	16	10	130	<0.01	16	<10	26
43811	<1	0.11	<10	5.7	<5	1.55	2	105	1192	2	5.35	<0.01	23.09	882	<2	0.02	2188	24	16	154	<0.01	19	<10	28
43812	<1	0.63	<10	5.1	<5	2.90	2	95	1262	6	4.76	0.01	22.20	1019	<2	0.02	2054	17	30	355	0.03	26	<10	37
43813	3	0.09	<10	5.9	<5	0.46	13	99	1244	152	5.40	<0.01	23.53	1033	<2	0.01	2140	20	879	19	<0.01	15	<10	2202
43814	1	0.13	<10	5.5	<5	1.46	8	93	1192	32	5.20	0.02	21.93	801	<2	0.01	1986	16	260	98	<0.01	16	<10	1243
43815	<1	0.06	<10	5.6	<5	0.88	4	110	1058	5	5.31	<0.01	23.68	775	<2	0.01	2299	22	21	52	<0.01	15	<10	56
43816	<1	0.09	<10	5.5	<5	0.80	2	96	1143	10	5.10	0.01	22.98	672	<2	0.02	2085	22	46	69	<0.01	15	<10	54
43822	<1	0.18	13	5.9	<5	0.81	2	104	1521	19	5.46	0.02	24.03	903	<2	0.02	2157	36	18	26	0.01	18	<10	74
43823	<1	0.11	<10	6.1	<5	1.73	2	103	1387	21	5.61	0.02	24.54	1072	<2	0.02	2345	15	19	35	<0.01	17	<10	71
43832	<1	0.09	<10	6.2	<5	1.08	2	115	1581	5	5.90	<0.01	23.61	1098	<2	0.01	2393	14	19	45	<0.01	15	<10	37
43833	<1	1.16	<10	5.5	<5	2.74	2	96	1359	7	5.24	<0.01	20.32	1509	<2	0.01	1903	125	25	228	0.06	45	<10	56
43834	<1	2.32	<10	6.0	<5	2.88	2	86	1303	6	5.73	<0.01	19.54	1327	<2	0.01	1665	248	9	213	0.12	80	<10	40
43835	<1	0.10	<10	5.1	<5	2.21	2	102	1432	12	4.88	<0.01	21.07	1127	<2	0.01	2142	15	19	140	<0.01	15	<10	35
43836	<1	0.14	<10	5.8	<5	1.24	2	111	1300	6	5.67	<0.01	24.51	872	<2	0.01	2301	17	19	40	<0.01	18	<10	24
43837	<1	0.09	<10	5.5	<5	0.99	2	106	1111	<1	5.31	<0.01	23.84	941	<2	0.01	2176	15	14	37	<0.01	14	<10	22
43838	<1	0.08	<10	5.8	<5	0.55	2	110	1319	<1	5.58	<0.01	23.96	893	<2	0.01	2207	16	12	23	<0.01	15	<10	23
43839	<1	0.11	<10	6.1	<5	0.31	2	109	1478	2	5.82	<0.01	25.07	806	<2	0.01	2151	<10	14	21	<0.01	16	<10	21
43840	<1	0.09	<10	5.5	<5	0.01	2	103	1129	5	5.26	<0.01	23.80	790	<2	0.01	2193	19	15	8	<0.01	14	<10	18
43841	<1	0.12	11	5.7	<5	0.07	2	105	1111	3	5.40	0.02	24.21	801	<2	0.01	2201	17	14	14	<0.01	15	13	19
43842	<1	0.08	<10	5.4	<5	0.08	2	103	1277	8	5.22	<0.01	23.77	800	<2	0.01	2156	19	12	14	<0.01	12	10	20
43843	<1	0.08	<10	5.6	<5	0.09	2	109	1263	6	5.44	<0.01	24.09	828	<2	0.01	2304	16	13	16	<0.01	14	12	21
43844	<1	0.08	<10	6.0	<5	0.28	4	114	1219	1	5.70	<0.01	23.65	942	<2	0.01	2398	17	14	25	<0.01	14	<10	29
43845	<1	0.08	<10	5.6	<5	0.30	2	112	1549	<1	5.45	<0.01	23.98	885	<2	0.01	2420	13	9	26	<0.01	13	<10	26

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2333RR

Date : Jul-11-08

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
43846	<1	0.10	<10	5.5	<5	0.39	2	103	1217	1	5.25	<0.01	24.36	889	<2	0.01	2202	23	11	29	<0.01	15	<10	25
43847	<1	0.11	<10	5.8	<5	0.22	2	107	1340	1	5.49	<0.01	25.24	943	<2	0.01	2231	23	11	28	<0.01	14	<10	23
43848	<1	0.12	<10	5.8	<5	0.23	2	107	1133	3	5.40	<0.01	24.43	830	<2	0.01	2264	18	10	21	<0.01	17	<10	21
43849	<1	0.12	<10	5.9	<5	0.29	2	110	1278	1	5.62	0.01	25.20	929	<2	0.01	2264	15	13	25	<0.01	17	10	27
43850	<1	0.12	<10	5.7	<5	0.34	2	108	1143	2	5.66	0.01	25.37	888	<2	0.02	2222	16	13	34	<0.01	17	10	26
43851	<1	0.09	<10	5.8	<5	0.03	2	114	1076	2	5.47	0.01	25.37	952	<2	0.01	2352	17	15	31	<0.01	15	<10	28
43852	<1	0.08	<10	6.2	<5	0.07	2	118	1756	4	5.90	<0.01	26.11	976	<2	0.01	2339	20	16	57	<0.01	12	13	35
43853	<1	0.11	<10	5.9	<5	0.13	2	111	1637	2	5.53	<0.01	24.37	785	<2	0.02	2296	12	13	47	<0.01	14	13	30
43854	<1	0.09	34	6.0	<5	0.04	2	114	1456	3	5.68	0.03	25.68	891	<2	0.01	2386	23	18	28	<0.01	12	<10	29
43855	<1	0.10	<10	5.7	<5	0.03	2	110	1458	2	5.43	0.01	24.94	810	<2	0.01	2279	17	14	22	<0.01	13	<10	27
43856	<1	0.09	<10	6.0	<5	0.26	2	114	1412	2	5.56	0.12	25.96	870	<2	0.01	2381	22	15	31	<0.01	13	<10	28
43857	<1	0.11	<10	5.8	<5	0.45	2	106	1680	6	5.44	<0.01	24.92	792	<2	0.02	2186	22	14	42	<0.01	14	<10	29
43858	<1	0.10	<10	5.9	<5	0.26	2	119	1396	4	5.66	0.01	25.30	878	<2	0.01	2411	21	12	29	<0.01	16	11	37
43859	<1	0.10	<10	5.8	<5	0.29	3	107	1208	1	5.48	<0.01	23.99	718	<2	0.01	2166	15	8	28	<0.01	15	11	25
43860	<1	0.08	<10	6.0	<5	0.07	2	111	1635	<1	5.55	<0.01	23.88	834	<2	0.01	2256	16	11	18	<0.01	12	10	26
43861	<1	0.11	<10	5.8	<5	0.15	2	109	2094	<1	5.28	<0.01	23.78	911	<2	0.01	2203	21	12	18	<0.01	12	<10	36
43862	<1	0.11	<10	5.4	<5	0.39	5	104	1530	<1	5.08	<0.01	23.61	806	<2	0.01	2139	15	8	24	<0.01	13	10	27
43863	<1	0.10	<10	5.6	<5	0.38	2	104	1498	1	5.31	<0.01	23.90	839	<2	0.01	2131	14	10	23	<0.01	13	<10	24
43864	<1	0.34	<10	5.8	<5	0.56	2	108	1822	<1	5.51	<0.01	24.59	901	<2	0.01	2011	42	11	31	0.01	17	<10	40
43865	<1	0.09	<10	5.9	<5	1.07	2	105	1390	<1	5.55	0.01	23.07	849	<2	0.01	1955	12	9	38	<0.01	14	<10	32
43866	<1	0.10	<10	6.3	<5	1.30	3	114	1517	9	5.75	0.01	22.53	1222	<2	0.01	2117	15	168	49	<0.01	13	<10	234
43867	<1	0.03	32	6.1	<5	0.66	2	111	610	<1	5.75	0.01	23.18	1127	<2	0.01	2034	14	26	39	<0.01	13	<10	31
43868	5	4.68	11	6.6	<5	1.48	26	58	580	210	5.98	0.03	15.75	2863	<2	0.05	727	800	6572	94	0.17	109	<10	4220
43888	<1	0.09	<10	5.9	<5	<0.01	2	104	1443	<1	5.63	<0.01	24.47	956	<2	0.01	2026	13	19	3	<0.01	14	<10	24
43889	<1	0.08	<10	5.8	<5	0.04	2	110	1889	<1	5.44	0.01	25.22	1002	<2	0.01	1996	19	16	13	<0.01	10	12	26
43890	<1	0.06	<10	5.1	<5	0.06	1	108	1780	<1	4.80	<0.01	24.60	945	<2	0.01	2033	14	8	19	<0.01	7	<10	20
43891	<1	0.08	<10	5.8	<5	0.09	2	106	2713	<1	5.50	<0.01	24.75	991	<2	0.01	1965	18	12	17	<0.01	6	13	26
43892	<1	0.06	<10	5.8	<5	<0.01	2	109	1846	<1	5.55	<0.01	24.82	848	<2	0.01	1942	14	14	7	<0.01	10	10	18
43893	<1	0.07	<10	6.0	<5	0.02	2	107	1763	<1	5.78	<0.01	24.92	844	<2	0.01	1942	20	23	6	<0.01	11	<10	32
43894	<1	0.04	<10	5.6	<5	0.05	2	107	964	<1	5.22	<0.01	24.62	774	<2	0.01	1966	14	12	9	<0.01	11	13	17

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2333RR

Date : Jul-11-08

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
43895	<1	0.04	<10	5.7	<5	<0.01	2	105	893	<1	5.34	<0.01	25.15	773	<2	0.01	1991	22	14	8	<0.01	11	14	15
43896	<1	0.05	<10	5.9	<5	<0.01	2	103	1133	<1	5.62	<0.01	24.52	792	<2	0.01	1985	16	12	7	<0.01	11	11	14
43897	<1	0.04	<10	5.8	<5	<0.01	2	113	828	<1	5.58	<0.01	25.48	841	<2	0.01	2073	14	13	6	<0.01	11	<10	14
43898	<1	0.05	<10	5.9	<5	0.01	2	113	726	<1	5.54	<0.01	24.72	860	<2	0.01	1997	18	10	6	<0.01	12	11	14
43899	<1	0.12	<10	6.4	<5	0.10	2	108	698	<1	6.01	0.01	23.41	775	<2	0.01	2041	26	13	17	0.01	16	<10	15
43900	<1	0.03	<10	6.0	<5	0.01	2	107	1269	<1	5.88	0.01	24.94	887	<2	0.01	2015	16	12	11	<0.01	10	12	20
43901	<1	0.06	<10	5.8	<5	<0.01	2	107	2290	<1	5.58	0.01	24.80	853	<2	0.01	2037	15	15	10	<0.01	7	<10	34
43902	<1	0.04	<10	5.9	<5	0.01	2	107	1160	<1	5.52	<0.01	25.01	849	<2	0.01	2072	12	13	22	<0.01	9	12	20
43903	<1	0.04	<10	5.4	<5	<0.01	2	107	649	<1	5.13	<0.01	24.92	829	<2	0.01	2050	<10	11	7	<0.01	11	<10	19
43904	<1	0.05	<10	5.9	<5	0.01	2	112	1024	<1	5.58	0.01	25.71	973	<2	0.01	2174	19	9	16	<0.01	11	<10	18
43905	<1	0.10	<10	5.5	<5	0.45	2	105	1781	<1	5.09	<0.01	23.75	897	<2	0.01	1828	15	11	18	<0.01	12	<10	22
43906	<1	0.12	<10	5.7	<5	0.26	2	115	1680	<1	5.23	<0.01	25.71	924	<2	0.01	2108	18	16	31	<0.01	13	<10	22
43907	<1	0.08	<10	6.5	<5	0.06	2	110	2006	<1	6.21	0.01	25.42	952	<2	0.01	2348	25	41	40	<0.01	9	<10	24
43908	<1	0.09	82	6.0	<5	0.45	2	109	1386	<1	5.56	0.01	25.06	843	<2	0.01	2277	25	17	560	<0.01	13	<10	20
43909	<1	0.08	95	6.6	<5	0.06	2	113	2039	<1	6.26	0.01	27.06	925	<2	0.01	2394	31	23	1026	<0.01	9	10	27
43910	<1	0.11	28	6.1	<5	0.48	2	123	2502	<1	5.88	0.02	26.27	1067	<2	0.01	2349	23	29	283	<0.01	8	<10	31
43911	<1	0.07	11	6.6	<5	0.15	2	114	1750	<1	6.34	0.01	26.58	913	<2	0.01	2354	25	20	100	<0.01	10	<10	25
43912	<1	0.12	<10	6.0	<5	0.53	2	137	2259	<1	5.70	0.02	25.99	1039	<2	0.02	2266	32	30	28	<0.01	11	<10	30
43913	<1	0.11	<10	5.5	<5	1.09	1	137	2268	<1	5.07	0.01	25.56	1242	<2	0.02	2302	28	32	55	<0.01	11	<10	31
43914	<1	0.08	14	5.4	<5	2.49	2	130	2598	<1	5.01	0.01	22.12	1102	<2	0.01	2063	23	33	211	<0.01	7	<10	40
43915	<1	7.45	436	5.4	<5	1.11	1	41	329	<1	4.81	1.21	11.73	809	<2	2.23	381	816	<2	299	0.31	151	<10	38
43916	<1	0.25	<10	5.8	<5	0.95	2	104	1184	<1	5.59	0.01	23.30	997	<2	0.02	1977	41	12	39	0.01	17	<10	27
43917	<1	0.12	<10	5.9	<5	0.07	2	102	1006	<1	5.70	0.01	24.24	811	<2	0.02	2144	24	14	8	0.01	14	11	25
43918	<1	0.15	<10	5.5	<5	<0.01	2	108	1384	<1	5.28	0.01	25.16	888	<2	0.01	2070	22	14	1	<0.01	15	<10	29
43919	<1	0.14	<10	5.7	<5	0.10	2	107	1345	<1	5.47	0.01	24.81	982	<2	0.01	2139	22	16	23	<0.01	14	<10	31
43920	<1	7.88	1817	8.4	<5	4.32	1	37	210	14	5.82	3.50	3.35	1025	<2	2.48	63	2806	26	1087	0.64	180	<10	83
43921	<1	0.12	<10	5.6	<5	0.03	2	112	1218	<1	5.47	0.02	24.52	852	<2	0.02	2117	22	13	26	<0.01	13	<10	22
43922	<1	0.13	13	5.5	<5	0.14	2	128	2032	<1	5.22	0.02	25.29	1145	<2	0.02	2253	32	18	50	0.01	12	<10	34
43923	<1	0.09	<10	6.0	<5	0.27	2	114	1754	<1	5.82	0.01	25.37	962	<2	0.01	2209	19	22	37	<0.01	12	<10	26
43924	<1	0.11	<10	6.3	<5	0.72	2	107	2176	<1	5.79	0.01	23.19	957	<2	0.02	2107	20	19	125	<0.01	11	<10	24

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2333RR

Date : Jul-11-08

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
43925	<1	2.59	<10	6.3	<5	1.72	2	87	1403	11	5.80	0.01	18.95	948	<2	0.02	1521	278	22	138	0.12	71	<10	41
43926	<1	8.42	285	7.0	<5	1.83	1	57	464	<1	6.34	1.19	15.53	1572	<2	0.46	622	980	21	118	0.34	218	<10	68
43927	<1	0.17	<10	5.2	<5	5.73	2	94	1342	<1	4.75	0.01	18.93	1037	<2	0.02	1977	23	24	86	<0.01	17	<10	34
43928	<1	1.33	<10	5.4	<5	7.47	2	85	1513	<1	4.85	0.03	15.31	806	<2	0.04	1840	142	25	122	0.08	59	<10	46
43929	<1	0.11	<10	5.7	<5	3.21	2	109	1586	<1	5.49	0.01	22.96	903	<2	0.01	2197	29	15	46	<0.01	14	<10	37
43930	<1	0.11	<10	5.4	<5	4.67	2	106	1209	<1	5.13	0.01	22.19	970	<2	0.01	2014	27	12	158	<0.01	16	<10	26
43931	1	0.64	75	<0.5	<5	6.53	<1	90	1466	5	5.24	0.27	19.03	965	2	0.05	1813	94	8	91	0.02	26	<10	35
43932	<1	9.93	785	1.3	<5	3.95	3	36	134	23	6.06	2.05	5.59	3927	<2	2.63	77	2057	262	780	0.55	236	<10	450
43933	<1	0.19	37	<0.5	<5	1.95	<1	82	1568	3	4.93	0.01	22.85	1214	<2	0.02	1745	43	14	77	0.01	12	<10	60
43934	<1	0.25	37	<0.5	<5	0.99	<1	100	1885	8	5.68	0.01	24.59	1109	<2	0.01	2163	43	9	97	<0.01	11	<10	25
43935	1	0.08	41	<0.5	<5	0.01	1	100	1568	6	6.26	0.01	27.17	916	<2	0.01	2136	50	12	63	<0.01	7	<10	28
43936	1	0.10	38	<0.5	<5	<0.01	1	95	1220	3	6.24	0.01	25.56	785	<2	0.01	2035	42	11	34	<0.01	9	<10	25
43937	1	0.11	40	<0.5	<5	0.02	<1	97	1579	3	5.89	0.01	26.41	920	<2	0.01	2058	44	14	77	<0.01	7	<10	26
43938	1	0.06	43	<0.5	<5	0.01	1	105	1275	1	6.80	0.01	28.04	879	<2	0.01	2295	49	22	92	<0.01	5	<10	24
43939	1	0.02	41	<0.5	<5	0.22	1	101	674	1	5.90	0.01	27.14	895	<2	0.01	2156	45	14	119	<0.01	6	<10	20
43940	1	0.04	40	<0.5	<5	0.27	1	98	895	<1	5.30	0.01	26.65	913	<2	0.01	2175	44	11	69	<0.01	5	<10	20
43941	1	0.08	38	<0.5	<5	0.34	<1	89	1140	3	5.48	0.01	25.37	995	<2	0.01	1990	41	15	69	<0.01	7	<10	29
43942	<1	0.13	40	<0.5	<5	0.77	<1	88	1599	1	5.45	0.01	25.70	1003	<2	0.01	1966	43	11	96	<0.01	10	<10	33
43943	1	0.14	38	<0.5	<5	1.80	<1	94	2514	1	6.30	0.01	23.58	1185	<2	0.01	1952	45	18	111	<0.01	6	<10	51
43944	1	0.47	40	<0.5	<5	1.18	1	100	1940	12	5.82	0.01	24.80	1130	<2	0.01	2123	70	37	192	0.01	10	<10	226
43945	1	0.12	40	<0.5	<5	0.77	<1	91	1352	1	6.17	0.01	26.20	928	<2	0.01	2026	53	19	96	<0.01	6	<10	29
43946	1	0.07	41	<0.5	<5	0.19	<1	92	1330	<1	5.81	0.01	26.51	931	<2	0.01	2056	48	14	78	<0.01	4	<10	33
43947	2	0.05	43	<0.5	<5	0.05	1	102	928	1	5.93	0.01	27.83	761	<2	0.01	2271	46	7	71	<0.01	5	<10	18
43948	<1	0.05	41	<0.5	<5	<0.01	1	99	910	2	6.15	0.01	27.23	790	<2	0.01	2222	43	9	75	<0.01	5	<10	12
43949	1	0.06	41	<0.5	<5	<0.01	1	101	1027	2	5.93	0.01	28.07	829	<2	0.01	2203	44	11	56	<0.01	5	<10	13
43950	1	0.09	41	<0.5	<5	0.19	<1	96	1139	<1	5.79	0.01	26.66	863	<2	0.01	2106	47	9	57	<0.01	8	<10	14
43951	<1	0.07	46	<0.5	<5	0.07	<1	94	1167	2	5.86	0.01	26.35	843	<2	0.01	2124	44	10	38	<0.01	7	<10	13
43952	1	0.08	40	<0.5	<5	0.06	<1	95	1709	1	6.14	0.01	26.31	935	<2	0.01	2147	45	15	45	<0.01	4	<10	16
43953	<1	0.07	41	<0.5	<5	0.01	<1	98	1557	1	5.90	0.01	27.18	934	<2	0.01	2144	51	13	66	<0.01	4	<10	15
43954	1	0.13	41	<0.5	<5	0.02	<1	112	3041	<1	6.54	0.01	26.48	1070	<2	0.01	2252	51	11	54	<0.01	3	<10	31

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2333RR

Date : Jul-11-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
43955	1	0.16	39	<0.5	<5	0.07	<1	108	3103	2	6.26	0.01	26.33	1034	<2	0.01	2197	36	20	6	<0.01	2	<10	26
43956	1	0.10	39	<0.5	<5	0.03	<1	94	2146	<1	5.94	0.01	26.57	872	<2	0.01	2091	38	16	29	<0.01	2	<10	13
43957	1	0.08	41	<0.5	<5	0.03	<1	100	2003	<1	6.10	0.01	27.80	882	<2	0.01	2159	41	10	52	<0.01	2	<10	15
43958	<1	0.11	39	<0.5	<5	0.02	<1	95	2004	<1	5.52	0.01	27.11	875	<2	0.01	2228	39	18	36	<0.01	4	<10	15
43959	1	0.14	39	<0.5	<5	0.31	<1	88	2266	<1	5.67	0.01	25.36	1085	<2	0.01	1635	35	9	54	<0.01	7	<10	23
43960	1	0.05	40	<0.5	<5	0.06	1	101	1092	<1	6.09	0.01	26.72	1149	<2	0.01	2157	39	16	58	<0.01	7	<10	20
43961	1	0.07	42	<0.5	<5	0.17	<1	98	1359	<1	5.89	0.01	27.62	1228	<2	0.01	2125	34	13	90	<0.01	6	<10	23
43962	<1	0.07	42	<0.5	<5	0.08	1	98	1803	<1	5.98	0.01	27.29	1255	<2	0.01	2044	42	11	96	<0.01	5	<10	33
43963	1	0.08	42	<0.5	<5	0.09	<1	108	2809	<1	7.22	0.01	28.72	1331	<2	0.01	2277	46	18	85	<0.01	3	<10	45
43964	1	0.05	51	<0.5	<5	0.17	<1	93	1840	<1	6.46	0.01	26.48	1171	<2	0.01	2005	44	19	245	<0.01	4	<10	33
43965	<1	0.06	45	<0.5	<5	0.11	<1	91	1769	<1	6.38	0.01	27.07	1017	<2	0.02	2048	46	19	322	<0.01	4	<10	34
43966	1	0.05	40	<0.5	<5	<0.01	1	96	1537	<1	6.28	0.01	27.51	1013	<2	0.01	2143	43	16	55	<0.01	4	<10	29
43967	<1	0.06	39	<0.5	<5	<0.01	1	94	1625	<1	6.12	0.01	25.93	960	<2	0.01	2052	42	14	51	<0.01	4	<10	26
43968	<1	0.12	40	<0.5	<5	<0.01	1	102	1388	<1	6.19	0.01	26.28	788	<2	0.01	2144	46	41	73	<0.01	9	<10	23
43969	1	0.12	40	<0.5	<5	<0.01	1	94	1365	<1	5.72	0.01	25.51	823	<2	0.01	1988	47	14	70	<0.01	9	<10	20
43970	<1	1.15	44	<0.5	<5	0.77	1	101	1936	19	6.83	0.01	23.10	995	<2	0.01	2198	154	14	114	0.05	31	<10	32
43971	<1	1.28	47	<0.5	<5	1.11	<1	75	1289	<1	5.69	0.02	24.26	896	<2	0.01	1648	167	16	190	0.07	42	<10	24
43972	<1	0.10	41	<0.5	<5	0.44	<1	91	1566	<1	5.66	0.01	25.71	823	<2	0.01	1977	41	9	76	<0.01	6	<10	21
43973	<1	0.46	42	<0.5	<5	1.40	1	92	1356	<1	6.09	0.01	23.84	860	<2	0.01	1949	75	13	190	0.02	21	<10	22
43974	1	0.13	42	<0.5	<5	1.17	<1	89	1658	<1	5.33	0.01	24.66	881	<2	0.01	1971	42	17	150	<0.01	7	<10	41
43975	<1	0.14	45	<0.5	<5	1.91	1	86	1548	11	5.48	0.01	21.84	1026	<2	0.01	1815	45	29	262	<0.01	8	<10	61
43976	<1	0.27	45	<0.5	<5	4.84	4	75	1496	27	4.85	0.01	16.55	766	<2	0.03	1608	44	33	494	<0.01	8	<10	92
43977	<1	8.08	1934	1.9	<5	4.28	3	43	295	52	7.02	3.52	6.15	1823	<2	1.65	176	3115	121	879	0.71	193	<10	181
43978	<1	4.82	1240	1.4	<5	2.67	1	59	898	20	6.18	2.21	13.26	1127	<2	1.40	924	1682	20	704	0.38	110	<10	72
43979	<1	0.11	<10	5.7	<5	0.52	2	106	1239	<1	5.33	<0.01	23.41	842	<2	0.01	2145	12	16	44	<0.01	14	<10	42
43980	<1	0.09	<10	5.6	<5	0.91	2	102	975	<1	5.25	<0.01	22.42	771	<2	0.01	2066	18	16	36	<0.01	16	<10	32
43981	<1	0.09	<10	5.7	<5	0.88	2	99	1339	<1	5.36	<0.01	22.93	685	<2	0.01	2135	14	14	15	<0.01	14	<10	22
43982	<1	0.71	<10	5.7	<5	1.14	2	95	1383	<1	5.37	<0.01	22.33	873	<2	0.01	1953	66	13	17	0.04	33	<10	25
43983	<1	0.07	<10	5.1	<5	1.92	2	91	1392	<1	4.88	<0.01	21.53	877	<2	0.01	1962	17	13	10	<0.01	10	<10	24
43984	<1	0.09	<10	5.4	<5	3.65	2	92	1679	<1	4.73	<0.01	20.48	862	<2	0.02	1980	26	11	35	<0.01	12	<10	32

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2333RR

Date : Jul-11-08

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
43985	<1	7.49	873	7.8	<5	3.62	1	53	1611	59	6.54	1.95	5.69	2028	<2	2.28	701	1005	61	436	0.37	176	<10	179
43986	<1	9.25	856	6.6	<5	2.62	1	32	53	18	5.41	3.07	2.98	2246	<2	2.69	35	1010	32	674	0.41	200	<10	178
43987	<1	9.25	419	7.2	<5	2.68	1	40	45	12	6.43	1.94	4.78	1404	<2	2.70	34	881	23	630	0.49	286	<10	83
43988	<1	0.30	10	4.7	<5	4.72	2	74	1201	<1	4.28	0.04	17.19	796	<2	0.05	1563	36	13	62	0.01	21	<10	24
43989	<1	0.11	<10	5.5	<5	2.04	2	103	1323	<1	5.07	0.01	22.14	864	<2	0.02	2179	18	10	40	0.01	13	<10	23
43990	<1	0.08	<10	5.6	<5	0.82	2	104	1738	<1	5.18	<0.01	23.78	738	<2	0.01	2203	21	12	13	<0.01	10	10	23
43991	<1	0.08	<10	5.5	<5	0.52	2	113	1016	<1	5.29	<0.01	25.47	788	<2	0.01	2297	19	20	13	<0.01	13	<10	23
43992	<1	0.12	<10	5.9	<5	0.30	2	106	1508	<1	5.47	<0.01	23.04	639	<2	0.01	2206	13	14	11	<0.01	15	<10	27
43993	<1	0.13	<10	6.0	<5	0.62	2	107	1343	<1	5.58	<0.01	23.86	645	<2	0.01	2119	16	10	12	<0.01	18	<10	17
43994	<1	0.14	<10	5.9	<5	0.76	2	107	1826	<1	5.50	<0.01	24.26	644	<2	0.01	2187	17	13	11	<0.01	16	<10	22
43995	<1	0.38	<10	5.6	<5	2.12	2	99	1636	<1	5.18	<0.01	21.83	765	<2	0.01	1891	44	14	33	0.02	23	<10	25
43996	<1	6.81	322	5.8	<5	0.92	1	68	581	104	5.18	1.14	15.40	652	9	0.10	793	701	3	136	0.20	132	<10	34
43997	<1	6.30	410	6.1	<5	1.88	1	68	839	<1	5.39	1.57	13.89	672	4	0.09	957	725	3	213	0.21	157	<10	39
43998	<1	0.27	<10	5.2	<5	2.03	2	92	1409	<1	4.78	0.01	20.10	599	<2	0.02	1950	40	18	202	0.01	18	<10	14
43999	<1	0.13	<10	5.1	<5	1.10	1	99	1019	<1	4.72	0.01	21.54	554	<2	0.01	2039	18	11	196	0.01	17	<10	15
44000	<1	0.11	<10	6.2	<5	0.43	2	104	1413	<1	5.67	<0.01	23.32	540	<2	0.02	2211	<10	9	20	0.01	20	<10	16
Duplicates:																								
43803	<1	0.05	29	5.1	<5	1.15	2	101	695	6	4.65	0.01	21.05	801	<2	0.01	2110	24	14	322	<0.01	10	<10	24
43812	<1	0.61	<10	5.1	<5	2.82	4	93	1249	6	4.57	<0.01	21.52	981	<2	0.02	2031	<10	24	345	0.03	26	<10	33
43835	<1	0.11	<10	5.2	<5	2.21	2	102	1422	11	4.82	0.01	21.13	1126	<2	0.02	2123	17	18	141	<0.01	15	<10	35
43840	<1	0.09	<10	5.7	<5	0.01	2	105	1037	4	5.30	<0.01	24.12	797	<2	0.01	2237	20	13	8	<0.01	14	<10	18
43849	<1	0.13	<10	6.0	<5	0.30	2	113	1235	6	5.80	0.01	26.14	962	<2	0.01	2360	15	13	25	<0.01	18	10	27
43859	<1	0.10	<10	5.8	<5	0.30	2	106	1175	2	5.48	<0.01	24.17	717	<2	0.01	2180	13	12	28	<0.01	14	<10	20
43864	<1	0.33	<10	5.7	<5	0.55	2	108	1842	<1	5.44	<0.01	24.55	898	<2	0.01	2027	30	12	30	0.01	17	<10	35
43892	<1	0.05	<10	5.9	<5	<0.01	2	105	1679	<1	5.58	<0.01	24.75	843	<2	0.01	1933	16	13	7	<0.01	11	<10	17
43902	<1	0.04	<10	5.9	<5	0.01	2	106	1070	<1	5.51	<0.01	24.44	833	<2	0.01	2057	13	12	23	<0.01	9	10	19
43907	<1	0.09	<10	6.8	<5	0.06	2	118	2275	<1	6.46	0.01	26.86	1017	<2	0.01	2513	24	40	42	<0.01	10	<10	29
43916	<1	0.24	<10	5.9	<5	0.97	2	105	1250	<1	5.68	<0.01	23.62	1001	<2	0.01	2002	40	15	40	0.01	17	<10	25
43926	<1	8.69	289	7.1	<5	1.89	1	59	501	<1	6.26	1.22	16.05	1609	<2	0.51	643	1018	16	121	0.36	223	<10	69
43931	<1	0.67	79	<0.5	<5	6.86	1	91	1477	4	5.56	0.28	19.83	1021	2	0.05	1894	106	5	175	0.02	28	<10	37

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2333RR

Date : Jul-11-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
43940	<1	0.05	40	<0.5	<5	0.30	1	102	963	<1	5.46	0.01	27.47	943	<2	0.01	2256	42	3	57	<0.01	5	<10	19
43950	<1	0.08	41	<0.5	<5	0.20	1	95	1090	<1	6.01	0.01	26.64	860	<2	0.01	2101	45	11	72	<0.01	9	<10	13
43955	<1	0.17	41	<0.5	<5	0.07	<1	106	2783	<1	6.45	0.01	26.59	1044	<2	0.01	2163	47	16	50	<0.01	5	<10	28
43964	1	0.06	53	<0.5	<5	0.19	<1	97	1920	<1	6.85	0.01	28.13	1236	<2	0.01	2121	44	19	264	<0.01	4	<10	37
43974	<1	0.13	42	<0.5	<5	1.21	<1	91	1639	<1	5.45	0.01	25.29	904	<2	0.01	2016	41	12	150	<0.01	8	<10	34
43979	<1	0.11	<10	5.6	<5	0.52	2	104	1629	<1	5.31	0.01	23.49	846	<2	0.01	2129	20	20	44	<0.01	12	<10	38
43988	<1	0.32	10	5.0	<5	5.02	1	80	1237	<1	4.59	0.04	18.34	859	<2	0.05	1702	38	11	65	0.01	23	<10	33
43998	<1	0.24	<10	5.0	<5	1.91	1	85	1298	<1	4.43	0.02	18.76	562	<2	0.02	1829	25	8	189	0.01	17	<10	12
Standards:																								
Blank	<1	0.01	<10	<0.5	<5	<0.01	<1	1	5	<1	0.02	<0.01	0.01	<5	<2	0.01	1	<10	<2	<1	<0.01	<1	<10	<2
CH-4	2	7.57	471	6.7	<5	1.86	2	32	127	1991	5.50	1.79	1.44	464	<2	3.17	55	686	11	202	0.32	101	<10	215

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2360RR

Date : Nov-21-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
44001	<1	0.11	<10	7.0	<5	1.63	2	111	1638	<1	6.43	0.01	24.22	802	<2	0.02	2433	26	14	28	<0.01	18	11	26
44002	<1	0.13	<10	6.4	<5	1.66	2	112	1488	<1	5.88	0.01	25.66	932	2	0.02	2430	32	24	67	<0.01	21	13	33
44003	1	4.74	<10	5.9	<5	1.20	1	62	694	90	5.42	0.07	21.09	826	<2	0.14	928	470	48	55	0.20	113	11	53
44004	<1	0.13	<10	6.8	<5	0.76	2	109	1456	<1	6.17	0.01	25.98	920	<2	0.01	2387	21	16	33	<0.01	19	<10	25
44005	<1	0.21	<10	6.5	<5	1.01	2	106	1910	<1	6.13	0.01	25.43	928	<2	0.01	2301	27	11	52	0.01	20	18	30
44006	<1	6.92	11	5.3	<5	0.83	<1	56	596	<1	4.36	0.15	20.70	688	344	0.30	767	601	<2	63	0.27	144	12	39
44007	1	0.91	15	6.5	<5	0.39	2	100	2168	78	6.01	0.01	22.85	725	2	0.02	1939	100	13	20	0.03	36	18	24
44008	<1	0.27	<10	6.5	<5	0.47	1	112	2292	11	5.86	<0.01	23.61	834	4	0.01	2199	27	13	52	0.01	18	20	27
44009	<1	1.52	<10	5.4	<5	1.06	1	84	1698	1	4.60	0.01	22.64	1155	34	0.01	1778	124	14	41	0.04	32	10	63
44010	<1	0.13	<10	6.3	<5	0.41	2	114	2656	<1	5.79	<0.01	24.91	710	<2	0.01	2433	19	11	8	<0.01	16	15	23
44011	<1	0.11	<10	6.2	<5	0.79	2	112	1642	<1	5.46	<0.01	24.00	866	<2	0.01	2309	28	8	29	<0.01	19	14	22
44012	<1	7.79	<10	7.1	<5	0.72	1	63	641	<1	6.47	0.17	20.87	1408	<2	0.41	455	746	<2	32	0.42	246	15	41
44013	<1	0.16	<10	6.3	<5	0.38	2	109	1628	<1	5.74	<0.01	24.42	815	<2	0.01	2343	24	11	14	<0.01	16	14	21
44014	<1	0.05	<10	6.0	<5	0.17	2	111	875	<1	5.58	<0.01	25.67	906	<2	0.01	2364	28	8	3	<0.01	15	17	19
44015	<1	0.08	<10	6.3	<5	0.45	2	119	1534	<1	5.92	0.01	27.51	962	<2	0.01	2403	17	9	14	<0.01	12	14	22
44016	<1	0.08	<10	6.3	<5	0.44	2	112	975	<1	5.81	<0.01	25.11	941	<2	0.01	2248	14	111	24	<0.01	16	17	33
44017	<1	0.04	<10	6.6	<5	0.18	2	120	843	<1	5.96	<0.01	25.52	713	<2	0.01	2276	29	9	6	<0.01	12	15	12
44018	<1	0.02	<10	6.1	<5	0.02	2	128	502	<1	5.77	<0.01	26.61	697	<2	0.01	2399	26	12	3	<0.01	13	20	13
44019	<1	0.08	<10	7.0	<5	0.03	2	118	1432	<1	6.63	<0.01	26.09	742	<2	0.01	2434	32	19	1	<0.01	15	20	14
44020	<1	0.06	<10	6.3	<5	0.12	1	109	1218	22	5.75	<0.01	25.02	749	<2	0.01	2371	29	11	4	<0.01	13	12	16
44021	<1	0.14	23	6.0	<5	0.26	2	101	1726	11	5.51	0.01	25.56	789	<2	0.01	2218	38	6	31	<0.01	15	19	26
44022	<1	0.15	<10	5.6	<5	0.29	1	97	1872	<1	4.97	<0.01	23.87	869	<2	0.01	2025	23	13	12	<0.01	16	11	25
44023	1	0.75	<10	6.0	<5	0.69	5	164	1160	54	5.50	0.01	19.30	1672	<2	0.02	1393	73	1602	102	0.03	35	13	732
44024	<1	0.07	<10	5.7	<5	0.68	1	107	1378	<1	5.44	<0.01	24.45	760	<2	0.01	2198	24	34	43	<0.01	13	<10	43
44025	<1	0.07	34	4.8	<5	0.11	2	95	1166	<1	5.70	0.02	26.78	892	<2	0.51	2113	<10	17	22	<0.01	10	<10	17
44026	<1	0.14	32	5.2	<5	0.02	2	91	2115	<1	6.35	0.03	27.08	966	<2	0.73	2094	66	7	1	<0.01	11	<10	39
44027	<1	0.10	34	5.4	<5	0.01	2	98	1714	<1	6.38	0.03	28.01	1035	<2	0.83	2198	107	12	3	<0.01	10	<10	34
44028	<1	0.08	33	5.0	<5	0.62	2	96	1275	<1	6.00	0.03	26.90	1088	<2	0.72	2107	96	6	21	<0.01	10	<10	30
44029	<1	0.09	33	5.4	<5	0.07	2	92	1505	<1	6.28	0.03	26.72	1052	<2	0.63	2034	18	<2	3	<0.01	9	<10	33
44030	<1	0.08	32	5.0	<5	0.95	2	86	1330	<1	5.89	0.03	26.24	1006	<2	0.64	1926	73	8	33	<0.01	9	<10	25

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2360RR

Date : Nov-21-08

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
44031	<1	2.95	39	6.3	<5	0.30	2	88	1738	<1	7.22	0.02	22.37	1202	<2	0.44	1483	404	6	7	0.14	75	<10	44
44032	<1	0.81	31	5.3	<5	0.21	2	79	1927	<1	6.21	0.03	22.71	913	<2	0.49	1634	190	5	8	0.04	32	<10	25
44033	<1	0.12	31	5.0	<5	0.33	2	85	1214	18	5.47	0.02	23.62	795	<2	0.48	1724	48	6	11	<0.01	13	<10	42
44034	<1	9.47	394	7.8	<5	2.67	3	50	613	33	8.64	1.78	12.77	1513	4	0.81	410	969	<2	490	0.52	307	<10	55
44035	<1	9.39	386	7.1	<5	2.97	3	48	388	<1	7.78	1.93	11.77	2255	<2	0.99	364	943	78	315	0.49	284	<10	152
44036	<1	7.61	393	7.8	<5	2.65	7	52	449	129	8.61	1.35	11.73	4365	<2	0.90	541	799	321	286	0.41	261	<10	911
44037	<1	7.77	168	6.5	<5	1.34	2	54	471	4	7.13	0.60	17.23	1285	<2	0.37	861	896	5	97	0.29	212	<10	51
44038	<1	0.30	32	5.7	<5	1.50	2	87	1175	9	6.29	0.03	23.02	737	<2	0.51	2035	88	21	105	0.01	13	<10	23
44039	<1	0.09	31	5.2	<5	1.29	2	83	1065	13	6.06	0.03	24.31	848	<2	0.47	1966	<10	22	101	<0.01	10	<10	34
44040	<1	0.06	32	5.1	<5	0.66	2	81	1233	7	5.92	0.02	25.76	943	<2	0.37	1890	<10	9	39	<0.01	7	<10	21
44041	<1	0.05	34	5.2	<5	0.60	2	86	1124	<1	6.21	0.03	26.52	1016	<2	0.45	1979	58	11	46	<0.01	8	<10	22
44042	<1	0.08	35	5.6	<5	0.24	2	98	1445	<1	6.43	0.03	27.32	1022	<2	0.37	2143	73	13	4	<0.01	7	<10	17
44043	<1	0.06	36	5.5	<5	0.54	2	101	1301	<1	6.26	0.08	26.57	880	<2	0.32	2124	39	8	14	<0.01	9	<10	22
44044	<1	0.21	32	5.2	<5	0.22	2	89	1582	1	5.78	0.06	24.24	834	<2	0.20	1954	22	13	13	0.01	10	<10	17
44045	<1	12.94	621	8.2	<5	3.00	3	42	49	<1	9.30	1.52	13.34	1937	<2	0.92	56	1730	<2	1633	0.71	371	<10	34
44046	<1	0.77	33	5.0	<5	0.05	2	81	1149	<1	5.73	0.02	24.49	755	<2	0.25	1788	181	9	9	0.04	24	<10	10
44047	<1	0.24	43	4.8	<5	<0.01	2	91	1498	<1	5.62	0.03	26.19	878	<2	0.15	1960	72	5	20	0.01	10	<10	12
44048	<1	0.07	34	5.0	<5	<0.01	2	95	1866	<1	5.80	0.02	26.93	857	<2	0.18	1977	79	4	1	<0.01	4	<10	18
44049	<1	0.07	37	4.9	<5	0.11	2	90	1850	<1	5.85	0.04	27.46	901	<2	0.19	2064	20	23	11	<0.01	5	<10	32
44050	<1	0.07	35	5.2	<5	<0.01	2	97	2195	<1	5.92	0.03	27.75	881	<2	0.33	2154	160	25	13	<0.01	3	<10	31
44051	<1	1.39	272	5.3	<5	2.29	2	86	1728	1	5.64	0.63	22.19	1202	<2	0.66	1841	427	28	177	0.08	26	<10	51
44052	<1	2.09	35	5.3	<5	1.81	2	77	2724	<1	5.98	0.03	22.82	1041	<2	0.33	1760	333	17	63	0.13	63	<10	43
44053	<1	9.18	40	4.8	<5	0.12	1	32	34	2	5.07	0.04	21.00	903	<2	0.43	99	1349	<2	29	0.55	233	<10	47
44054	<1	5.89	37	5.3	<5	1.95	2	47	358	4	5.70	0.02	18.21	969	<2	0.17	684	939	2	146	0.36	181	<10	25
44055	<1	7.46	285	5.8	<5	2.69	2	41	268	2	6.52	1.14	11.49	1780	<2	1.26	526	1017	41	192	0.36	220	<10	82
44056	<1	9.97	736	6.9	<5	2.45	3	39	48	95	7.26	3.49	5.06	3740	<2	1.42	53	1311	205	322	0.52	313	<10	246
44057	<1	10.21	708	7.2	<5	2.72	3	40	34	129	7.32	3.70	4.23	2568	<2	1.74	35	1106	93	354	0.54	334	<10	209
44058	<1	10.06	580	7.8	<5	2.89	3	45	37	95	8.10	2.97	4.14	1458	<2	1.72	34	1217	44	385	0.54	329	<10	134
44059	<1	0.14	33	5.7	<5	1.84	2	90	1579	<1	5.94	0.02	23.92	971	<2	0.13	1927	112	25	37	0.01	11	<10	32
44060	<1	4.95	193	5.5	<5	1.58	2	56	299	<1	6.05	0.72	13.49	779	<2	1.00	1021	695	24	122	0.19	150	<10	45

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2360RR

Date : Nov-21-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
44061	<1	0.15	42	4.9	<5	2.30	2	84	489	5	5.25	0.08	25.34	1047	<2	0.31	2233	45	22	24	0.01	14	<10	44
44062	<1	0.08	41	4.5	<5	1.78	2	86	432	7	5.19	0.04	25.41	941	<2	0.20	2250	80	25	23	<0.01	10	<10	45
44063	<1	0.32	37	5.0	<5	2.12	2	88	1281	2	5.74	0.03	24.19	1046	<2	0.20	2075	17	18	40	0.02	16	<10	40
44064	<1	0.58	111	5.4	<5	2.11	2	93	1254	4	5.79	0.15	23.05	1029	<2	0.05	2086	291	38	108	0.04	22	<10	51
44065	<1	1.60	28	5.0	<5	6.81	2	85	1017	102	5.75	0.02	16.02	948	<2	0.17	1880	230	18	73	0.08	61	<10	34
44066	<1	2.49	636	6.5	<5	5.85	2	77	865	9	5.84	1.31	14.47	1273	<2	0.43	1465	1081	38	274	0.16	64	<10	53
44067	<1	10.26	612	7.3	<5	2.30	3	41	40	1	7.77	2.73	3.90	1183	<2	2.69	30	1155	34	352	0.54	328	<10	89
44068	<1	10.17	427	7.5	<5	0.27	3	41	47	127	8.17	1.56	9.20	899	<2	1.98	71	1050	<2	201	0.55	359	<10	27
44069	<1	9.95	764	5.5	<5	0.68	2	31	69	61	5.87	2.21	4.83	543	<2	3.01	91	1232	<2	274	0.42	235	<10	31
44070	<1	6.21	35	6.2	<5	1.52	3	74	669	125	6.92	0.04	17.22	827	<2	0.17	1152	824	8	25	0.35	189	<10	43
44071	<1	7.91	42	5.0	<5	0.47	2	62	836	31	5.50	0.07	19.26	927	<2	0.18	1095	1040	7	12	0.26	134	<10	56
44072	<1	2.04	36	4.7	<5	2.35	2	71	1074	<1	5.40	0.04	19.07	824	<2	0.07	1572	257	20	54	0.07	35	<10	46
44073	<1	0.15	<10	6.2	<5	2.55	2	101	1445	<1	5.44	0.01	20.68	977	<2	0.03	1998	25	15	42	<0.01	20	<10	29
44074	<1	3.16	<10	5.6	<5	0.90	1	83	901	14	4.96	0.01	21.60	717	<2	0.05	1558	305	2	30	0.08	46	<10	28
44075	<1	0.07	<10	6.5	<5	1.36	2	106	908	49	5.91	<0.01	23.60	797	<2	0.02	2213	27	8	13	<0.01	17	<10	20
44076	<1	0.09	<10	6.1	<5	1.31	2	108	982	43	5.82	<0.01	24.74	788	<2	0.02	2185	22	10	19	<0.01	16	<10	21
44077	<1	0.08	<10	6.1	<5	0.59	2	115	1003	108	5.84	<0.01	24.80	555	<2	0.02	2250	18	9	8	<0.01	17	<10	21
44078	<1	0.10	<10	6.1	<5	0.28	2	107	1316	91	5.69	<0.01	24.18	672	<2	0.01	2155	17	9	4	<0.01	16	10	22
44079	<1	0.08	<10	5.7	<5	0.13	2	110	1034	128	5.35	<0.01	24.55	801	<2	0.01	2177	15	10	11	<0.01	16	<10	29
44080	<1	0.09	13	5.8	<5	0.21	2	109	883	96	5.60	<0.01	24.96	757	<2	0.02	2244	24	21	19	<0.01	16	<10	28
44081	<1	0.05	<10	5.5	<5	0.77	2	105	1175	113	5.32	<0.01	23.99	664	<2	0.02	2208	21	10	13	<0.01	12	<10	23
44082	<1	0.09	<10	5.4	<5	0.91	2	98	997	31	5.09	0.01	23.43	643	<2	0.01	2119	21	11	31	<0.01	18	<10	23
44083	<1	0.30	<10	6.7	<5	0.72	2	109	1346	16	6.27	<0.01	22.12	942	<2	0.02	2241	60	11	9	0.01	21	<10	28
44084	<1	1.11	39	6.9	<5	1.09	2	100	1341	13	6.48	0.01	21.10	759	<2	0.05	2120	161	9	21	0.03	27	<10	31
44085	<1	0.02	<10	4.9	<5	1.59	1	107	384	8	4.70	<0.01	24.61	970	<2	0.02	2461	27	8	15	<0.01	12	<10	25
44086	<1	1.27	<10	5.4	<5	0.94	2	100	511	5	4.91	0.01	23.10	800	<2	0.02	2039	159	7	23	0.08	50	<10	29
44087	<1	0.05	<10	5.0	<5	0.50	2	126	544	<1	4.56	<0.01	20.58	464	<2	0.02	2078	21	9	11	<0.01	13	<10	26
44088	<1	0.15	<10	6.0	<5	0.68	2	155	1125	78	5.84	<0.01	17.16	263	<2	0.02	2298	22	12	15	<0.01	15	<10	30
44089	<1	8.76	<10	7.1	<5	0.56	1	57	497	66	6.43	0.01	20.16	1174	<2	0.38	694	1112	<2	26	0.26	115	<10	40
44090	<1	0.09	<10	5.3	<5	1.65	2	90	803	3	5.13	<0.01	17.17	482	<2	0.02	1898	38	8	33	<0.01	16	<10	22

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2360RR

Date : Nov-21-08

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
44091	<1	8.20	37	5.9	<5	0.79	<1	43	233	3	5.31	0.02	18.53	1247	<2	0.44	360	1021	<2	59	0.25	110	<10	41
44092	<1	0.10	<10	5.9	<5	2.93	2	102	1294	<1	5.41	0.01	20.68	1047	<2	0.03	1985	28	10	77	<0.01	15	<10	32
44093	<1	0.20	10	6.2	<5	2.00	2	96	1165	2	5.48	0.01	23.83	1138	<2	0.03	2110	39	11	43	<0.01	20	<10	34
44094	<1	0.32	<10	5.6	<5	1.47	2	107	1203	<1	5.12	0.01	20.09	655	<2	0.03	2012	56	27	102	0.01	21	<10	24
44095	<1	10.35	1469	6.6	<5	0.59	<1	34	56	115	6.07	4.20	8.08	1016	<2	1.18	64	1119	<2	139	0.42	221	<10	33
44096	<1	10.75	1903	7.0	<5	0.52	1	38	55	11	6.43	5.15	5.56	906	<2	1.38	35	1218	<2	177	0.44	236	<10	34
44097	<1	3.49	28	5.6	<5	0.08	1	75	737	<1	5.33	0.08	18.40	514	<2	0.04	1071	428	<2	16	0.19	91	<10	28
44098	<1	3.94	14	6.5	<5	0.61	2	87	1077	11	6.09	0.03	17.62	640	<2	0.05	1284	482	2	23	0.15	80	<10	31
44099	<1	6.90	194	6.4	<5	1.74	1	57	703	11	5.88	0.98	13.85	784	<2	1.32	742	816	<2	143	0.23	141	<10	39
44100	<1	2.91	38	6.1	<5	3.00	2	77	1042	24	5.63	0.16	16.74	729	<2	0.17	1384	319	7	83	0.12	74	<10	35
Duplicates:																								
44001	<1	0.11	<10	7.2	<5	1.67	2	114	1726	<1	6.51	0.01	24.88	817	<2	0.02	2488	23	17	29	<0.01	19	13	28
44010	<1	0.12	<10	6.1	<5	0.39	1	110	2445	<1	5.56	<0.01	23.82	678	<2	0.01	2349	20	10	8	<0.01	15	15	21
44020	<1	0.06	<10	6.3	<5	0.11	1	110	1212	17	5.86	<0.01	25.52	762	<2	0.01	2406	20	13	4	<0.01	13	21	15
44025	<1	0.06	35	4.9	<5	0.11	2	95	1152	<1	5.74	0.03	27.16	910	<2	0.32	2189	41	25	21	<0.01	8	<10	22
44034	<1	9.55	399	7.4	<5	2.69	3	49	537	41	8.17	1.80	12.89	1487	5	0.81	416	1020	<2	474	0.52	306	<10	57
44044	<1	0.22	33	5.4	<5	0.24	2	91	1238	3	6.09	0.11	25.50	873	<2	0.53	2046	132	8	12	0.01	13	<10	24
44049	<1	0.09	41	5.4	<5	0.13	2	94	1242	<1	6.12	0.06	28.36	957	<2	0.26	2134	179	28	12	0.01	11	12	45
44058	<1	10.06	580	7.8	<5	2.89	3	45	37	95	8.10	2.97	4.14	1458	<2	1.72	34	1217	44	385	0.54	329	<10	134
44068	<1	10.54	441	7.8	<5	0.28	3	42	74	122	8.56	1.60	9.48	925	<2	1.91	76	1363	2	210	0.59	370	<10	39
44073	<1	0.16	12	6.4	<5	2.69	2	104	1563	<1	5.76	0.02	21.70	1036	<2	0.03	2075	27	19	44	<0.01	22	<10	35
44082	<1	0.09	44	5.4	<5	0.91	2	97	961	30	5.11	0.01	23.38	646	<2	0.04	2078	18	11	30	<0.01	18	<10	25
44092	<1	0.08	<10	5.7	<5	2.83	2	99	1282	<1	5.27	0.01	20.04	1014	<2	0.02	1945	19	8	75	<0.01	15	<10	28
44097	<1	3.50	27	5.5	<5	0.09	1	73	775	<1	5.28	0.07	18.22	510	<2	0.13	1053	420	<2	16	0.18	90	<10	28
Standards:																								
Blank	<1	<0.01	<10	<0.5	<5	<0.01	<1	<1	1	2	0.03	0.01	0.01	<5	<2	<0.01	1	<10	<2	<1	<0.01	<1	<10	<2
CH-4	2	7.60	473	6.3	<5	1.92	2	31	141	1996	5.46	1.80	1.45	468	<2	3.25	56	707	10	204	0.33	101	<10	223

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2375RR

Date : Nov-24-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
044101	<1	0.15	<10	5.3	<5	2.43	2	82	1269	3	5.10	0.01	17.16	496	<2	0.04	1827	23	18	35	<0.01	19	<10	27
044102	<1	0.14	10	5.8	<5	2.36	2	95	1208	<1	5.34	0.01	21.75	1046	<2	0.02	2001	14	18	36	<0.01	19	11	38
044103	<1	0.19	<10	6.4	<5	4.20	2	96	1275	2	5.82	0.01	21.12	1251	<2	0.03	2068	21	20	98	0.01	24	<10	41
044104	<1	2.54	87	6.2	<5	1.62	2	87	957	12	5.67	0.25	19.62	835	<2	0.05	1534	331	14	75	0.13	69	<10	40
044105	<1	0.63	<10	5.4	<5	1.35	2	111	1426	6	5.15	0.01	21.65	928	<2	0.02	2184	119	13	17	0.03	25	<10	44
044106	<1	0.64	<10	5.7	<5	2.18	2	102	1506	4	5.34	0.01	21.27	1000	<2	0.02	1967	76	13	23	0.04	32	10	44
044107	<1	3.10	620	4.8	<5	1.29	1	75	446	37	4.51	0.74	15.34	1275	<2	0.34	1451	702	27	186	0.18	69	<10	101
044108	<1	4.35	294	6.6	<5	3.39	3	64	501	14	5.71	0.46	14.76	2059	<2	0.38	993	791	153	187	0.27	124	<10	439
044109	2	9.10	629	7.6	<5	2.77	16	42	52	70	6.51	1.73	3.68	3148	<2	3.34	35	985	1238	549	0.57	279	<10	2576
044110	1	8.64	481	9.1	<5	3.34	8	46	65	60	8.07	1.32	3.63	3387	<2	2.89	36	920	1037	483	0.52	275	<10	1342
044111	<1	8.53	476	10.5	<5	2.63	8	46	80	54	9.39	0.95	3.87	4748	<2	2.44	46	924	692	410	0.52	282	<10	1548
044112	<1	8.49	467	7.7	<5	5.18	6	40	66	21	6.59	1.14	3.37	3495	<2	3.16	37	923	657	613	0.51	289	<10	1219
044113	1	8.58	626	8.1	<5	4.35	11	39	69	43	6.98	1.19	3.46	3900	<2	2.80	38	902	1016	758	0.53	274	<10	1998
044114	<1	0.17	<10	7.0	<5	1.44	2	105	1432	<1	6.74	0.01	22.16	1280	<2	0.04	2112	43	29	42	0.01	25	<10	73
044115	<1	0.22	10	7.3	<5	2.82	2	111	1017	<1	6.96	0.02	19.98	1402	<2	0.05	2047	70	38	73	0.01	29	<10	67
044116	<1	2.59	<10	5.5	<5	1.27	1	79	859	<1	5.08	0.01	21.01	1210	<2	0.02	1552	308	24	46	0.11	55	<10	52
044117	<1	0.13	<10	5.7	<5	1.32	2	103	1461	<1	5.49	0.01	23.13	1227	<2	0.02	2113	21	20	40	0.01	18	<10	59
044118	<1	0.15	<10	6.2	<5	1.14	2	111	1077	<1	5.91	0.01	24.50	1089	<2	0.02	2248	24	20	21	<0.01	20	<10	51
044119	<1	0.13	<10	5.9	<5	1.56	2	102	943	2	5.57	0.01	22.55	1067	<2	0.02	2052	32	22	90	<0.01	18	<10	54
044120	<1	0.13	<10	5.3	<5	1.27	2	99	1054	<1	5.32	0.01	22.69	922	<2	0.01	2017	17	15	81	<0.01	17	<10	52
044121	<1	0.41	<10	5.7	<5	1.85	2	99	1204	<1	5.46	0.01	23.08	1226	<2	0.02	1931	43	26	102	0.02	20	<10	58
044122	<1	0.11	<10	5.8	<5	0.53	2	99	1085	<1	5.51	0.01	22.96	913	<2	0.02	2144	14	18	16	<0.01	19	<10	54
044123	<1	0.13	<10	6.4	<5	0.79	2	100	833	<1	5.91	0.01	24.05	935	<2	0.02	2181	35	19	30	<0.01	25	<10	49
044124	<1	2.37	12	6.9	<5	0.86	2	87	1100	22	6.72	0.01	20.03	1070	<2	0.02	1639	274	19	112	0.15	90	10	56
044125	<1	0.08	12	6.4	<5	1.55	2	105	2054	<1	6.02	0.01	22.29	1212	<2	0.02	2297	21	27	64	<0.01	20	<10	72
044126	<1	0.09	<10	6.1	<5	1.34	2	101	950	<1	5.84	0.01	22.13	1188	<2	0.01	2236	24	25	34	<0.01	19	<10	54
044127	<1	0.11	<10	6.3	<5	1.19	2	102	1252	<1	5.90	0.01	22.19	1117	<2	0.01	2228	25	22	30	<0.01	19	<10	62
044128	<1	0.14	<10	6.1	<5	0.89	2	105	3832	<1	6.06	0.01	22.19	1188	<2	0.01	2223	21	19	20	<0.01	21	<10	99
044129	<1	0.09	<10	5.8	<5	1.29	2	98	1358	<1	5.68	<0.01	22.04	1218	<2	0.01	2215	25	22	41	<0.01	19	10	53
044130	<1	0.12	<10	6.7	<5	1.57	2	107	1475	<1	6.34	0.01	23.17	1245	<2	0.01	2319	22	29	96	0.01	22	11	61

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2375RR

Date : Nov-24-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
044131	<1	0.08	<10	6.3	<5	1.11	2	102	1366	<1	5.88	0.01	21.82	1011	<2	0.02	2251	31	20	67	<0.01	20	<10	57
044132	<1	1.04	11	6.1	<5	3.16	2	79	1361	<1	5.59	0.01	19.82	1265	<2	0.02	1651	148	18	122	0.05	39	<10	55
044133	<1	0.06	84	6.2	<5	1.62	2	110	998	<1	5.80	0.01	23.10	1180	<2	0.02	2211	28	21	548	<0.01	18	<10	45
044134	<1	0.08	26	6.2	<5	2.13	2	91	1273	<1	5.65	0.01	20.25	1051	<2	0.02	1948	59	15	364	<0.01	20	<10	48
044135	<1	7.54	50	6.9	<5	2.70	1	56	343	<1	6.49	0.14	17.23	1363	<2	0.22	576	908	8	81	0.39	198	<10	61
044136	<1	10.63	1177	6.9	<5	3.98	<1	47	46	<1	6.00	3.37	6.13	1557	<2	1.49	178	1181	37	650	0.52	232	<10	177
044137	<1	9.72	700	6.3	<5	4.50	<1	46	167	<1	5.57	2.67	6.40	1206	<2	2.02	429	934	18	850	0.42	168	<10	127
044138	<1	7.89	197	6.4	<5	1.93	1	52	293	<1	5.87	1.00	15.43	1235	<2	0.49	614	694	17	116	0.31	158	<10	106
044139	<1	0.25	<10	6.6	<5	2.32	2	104	1358	<1	6.32	0.02	18.01	674	<2	0.04	2171	38	26	52	0.01	29	<10	44
044140	<1	3.10	15	4.4	<5	3.05	1	63	456	<1	4.17	0.04	18.78	1111	<2	0.02	1092	219	7	200	0.14	52	<10	39
044141	<1	0.24	<10	5.6	<5	4.61	2	89	1435	1	5.31	0.01	17.79	1079	<2	0.03	1843	28	17	279	0.01	23	<10	60
044142	<1	5.16	10	5.5	<5	3.21	1	56	481	<1	5.28	0.03	17.71	1165	<2	0.09	653	542	16	148	0.27	130	<10	82
044143	<1	1.17	13	5.1	<5	3.01	1	90	1063	9	4.87	0.01	19.08	1008	<2	0.02	1758	96	17	137	0.04	34	<10	49
044144	<1	0.16	<10	5.5	<5	2.21	2	81	1740	3	5.15	<0.01	20.89	1298	<2	0.02	1789	30	29	84	<0.01	18	<10	52
044145	<1	1.87	13	5.4	<5	1.24	1	79	1214	<1	5.02	0.01	20.62	1045	<2	0.02	1588	282	18	70	0.06	41	<10	58
044146	<1	1.44	15	6.3	<5	1.17	2	96	1217	<1	5.91	0.01	20.03	999	<2	0.03	1966	174	17	83	0.07	45	<10	52
044147	<1	13.01	3105	7.0	<5	1.17	<1	42	38	38	6.39	4.03	10.43	1765	<2	0.64	121	1591	31	194	0.48	224	13	82
044148	<1	3.78	77	6.3	<5	1.31	2	71	844	<1	5.84	0.02	18.18	1369	<2	0.06	1267	458	18	115	0.10	65	<10	58
044149	<1	8.25	185	7.9	<5	1.98	<1	53	316	<1	6.23	0.86	18.16	1186	<2	0.89	491	797	<2	87	0.35	203	<10	68
044150	<1	0.91	11	6.1	<5	3.89	2	87	1042	3	5.77	0.02	19.18	1308	<2	0.04	1818	118	31	111	0.04	43	<10	65
044151	<1	4.49	18	7.6	<5	3.43	2	75	718	26	7.08	0.06	18.40	1462	<2	0.14	1110	503	44	99	0.25	166	<10	74
044152	<1	3.06	12	7.2	<5	2.94	2	69	731	<1	6.54	0.02	16.25	1057	<2	0.09	1161	182	20	53	0.14	118	11	55
044153	<1	3.02	39	7.1	<5	2.18	2	76	605	3	6.41	0.09	16.36	1139	<2	0.14	1151	199	22	61	0.18	120	<10	57
044154	<1	3.91	33	8.3	<5	3.93	2	89	587	7	7.42	0.15	15.82	1234	<2	0.10	1366	308	61	67	0.21	170	<10	84
044155	<1	8.92	857	6.7	<5	3.62	1	35	42	148	5.61	1.92	3.46	1086	<2	4.38	39	1115	33	761	0.43	241	<10	134
044156	<1	9.13	963	6.7	<5	2.85	1	35	48	23	5.68	2.08	3.15	877	<2	4.80	35	1129	19	595	0.44	255	<10	109
044157	<1	6.28	250	7.2	<5	2.56	2	62	419	<1	6.48	1.15	12.21	1278	<2	1.38	769	709	24	239	0.32	197	<10	103
044158	<1	1.63	11	5.9	<5	3.69	2	80	818	9	5.55	0.03	16.03	871	<2	0.07	1547	192	169	100	0.08	58	<10	73
044159	<1	0.91	<10	5.6	<5	6.31	2	85	788	3	5.14	0.02	16.80	1188	<2	0.06	1609	123	59	135	0.03	31	<10	59
044160	<1	0.63	<10	5.9	<5	4.22	2	93	953	<1	5.30	0.01	18.87	1123	<2	0.04	1862	70	18	127	0.03	24	<10	59

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2375RR

Date : Nov-24-08

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
044161	<1	3.27	<10	6.1	<5	1.46	1	89	1115	4	5.63	0.04	17.34	1060	<2	0.04	1625	382	18	62	0.09	59	<10	67
044162	<1	7.22	68	7.4	<5	0.90	1	57	387	<1	6.62	0.35	15.85	2300	<2	0.71	630	879	29	80	0.32	223	<10	177
044163	<1	9.62	485	7.0	<5	1.60	1	35	49	<1	6.20	2.11	8.48	2050	<2	3.02	47	1152	14	738	0.46	274	<10	143
044164	<1	9.64	637	5.5	<5	2.47	1	31	47	<1	4.92	3.13	6.44	1238	<2	3.41	45	1156	9	918	0.42	230	<10	76
044165	<1	9.10	883	5.8	<5	3.16	1	36	127	<1	5.05	2.34	5.96	1172	<2	3.49	173	924	16	1167	0.41	223	<10	86
044166	<1	0.17	<10	4.6	<5	3.79	1	77	544	2	4.32	0.02	16.51	789	<2	0.05	1564	14	21	66	<0.01	18	<10	41
044167	<1	9.04	519	5.4	<5	2.76	1	40	122	<1	4.56	2.48	6.67	1001	<2	3.40	188	1020	9	859	0.42	186	<10	96
044168	<1	0.24	<10	7.1	<5	2.19	2	100	938	<1	6.30	0.02	21.99	1589	<2	0.04	1997	35	25	38	0.01	26	<10	61
044169	<1	0.18	<10	7.0	<5	0.89	2	102	996	<1	6.05	0.01	23.26	1666	<2	0.03	2020	12	21	19	0.01	23	13	71
044170	<1	0.09	<10	7.0	<5	0.51	2	109	962	<1	6.18	<0.01	23.46	1695	<2	0.01	2018	16	23	5	<0.01	21	<10	65
044171	<1	0.12	<10	7.1	<5	0.38	2	105	1289	<1	6.00	<0.01	23.37	1522	<2	0.01	1970	18	21	6	<0.01	19	<10	68
044172	<1	0.05	<10	6.5	<5	0.22	2	119	724	<1	6.00	0.01	25.09	1408	<2	0.01	2334	21	25	8	<0.01	15	<10	62
044173	<1	0.06	<10	6.1	<5	0.13	2	105	798	<1	5.47	0.01	22.66	1240	<2	0.02	2137	18	20	4	<0.01	12	<10	53
044174	<1	0.53	<10	6.0	<5	2.64	2	92	1022	3	5.63	0.01	20.97	1699	<2	0.02	1768	68	22	86	0.03	30	<10	52
044175	<1	0.78	<10	6.4	<5	1.48	2	96	1233	8	5.84	0.01	21.98	1197	55	0.02	1795	108	17	88	0.05	43	<10	47
044176	<1	7.17	<10	3.7	<5	0.59	<1	41	171	73	3.34	0.15	20.36	952	<2	0.35	532	339	2	27	0.36	133	<10	47
044177	<1	0.32	<10	5.8	<5	0.90	2	100	1097	3	5.66	<0.01	22.86	1196	<2	0.02	1995	28	19	34	0.01	25	<10	38
044178	<1	0.10	17	5.6	<5	0.58	2	99	1047	<1	5.35	0.01	23.90	1245	<2	0.02	2064	23	19	10	<0.01	16	<10	38
044179	<1	0.08	<10	5.9	<5	0.26	2	104	975	<1	5.49	<0.01	24.04	1071	<2	0.02	2162	16	21	17	<0.01	17	<10	36
044180	<1	0.10	13	5.3	<5	0.53	2	99	1020	4	5.18	<0.01	22.70	1048	<2	0.02	1990	26	21	46	<0.01	18	<10	35
044181	<1	0.08	<10	5.6	<5	0.45	2	107	968	3	5.45	0.01	24.24	805	<2	0.02	2220	17	19	4	<0.01	18	10	33
044182	<1	0.09	17	5.8	<5	0.93	2	104	1090	<1	5.62	<0.01	24.59	1281	<2	0.01	2124	22	24	23	<0.01	21	<10	35
044183	<1	0.12	<10	6.1	<5	0.17	2	109	1368	<1	5.79	0.01	25.80	1177	<2	0.01	2128	17	17	11	<0.01	19	<10	38
044184	<1	0.11	10	6.1	<5	0.38	2	117	1090	<1	5.89	0.01	26.49	1079	<2	0.02	2338	25	19	42	<0.01	20	<10	37
044185	<1	0.12	10	5.7	<5	0.64	2	105	1190	<1	5.50	0.01	25.54	1116	<2	0.02	2094	19	19	80	<0.01	21	<10	38
044186	<1	0.10	<10	6.5	<5	0.12	2	120	1352	<1	6.28	0.01	26.51	1120	<2	0.02	2291	22	19	22	<0.01	22	<10	40
044187	<1	0.12	<10	6.4	<5	0.17	2	103	1801	<1	6.07	0.01	25.42	900	<2	0.02	1805	20	21	33	<0.01	24	<10	35
044188	<1	0.14	<10	6.3	<5	0.05	2	115	1346	12	6.08	0.01	26.48	1092	<2	0.02	2365	22	18	23	<0.01	25	<10	36
044189	<1	0.11	<10	6.2	<5	0.02	2	114	1198	<1	5.87	<0.01	25.84	1063	<2	0.01	2265	18	17	14	<0.01	21	<10	35
044190	<1	0.13	<10	6.3	<5	0.36	2	108	1388	<1	5.95	0.01	25.05	1110	<2	0.02	2137	23	17	9	<0.01	20	<10	37

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

Assayers Canada
8282 Sherbrooke St., Vancouver, B.C., V5X 4R6
Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2375RR
Date : Nov-24-08

ICP-AES Report
Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
044191	<1	0.14	<10	6.8	<5	<0.01	2	120	3021	<1	6.60	<0.01	26.64	1309	<2	0.01	2331	29	20	10	<0.01	19	<10	50
044192	<1	0.12	16	6.4	<5	0.19	2	116	1493	<1	6.21	0.01	27.24	964	<2	0.02	2252	25	24	4	<0.01	21	<10	35
044193	<1	0.11	<10	6.0	<5	<0.01	2	110	1316	<1	5.76	<0.01	25.46	1046	<2	0.01	2215	17	18	3	<0.01	21	<10	33
044194	<1	0.14	<10	5.8	<5	<0.01	2	105	1333	15	5.50	<0.01	24.62	999	<2	0.01	2165	28	19	1	<0.01	20	10	32
044195	<1	0.12	<10	5.7	<5	0.07	2	107	1231	<1	5.54	<0.01	24.96	1145	<2	0.01	2192	19	19	1	<0.01	20	<10	32
044196	<1	0.13	<10	5.5	<5	0.02	2	97	1327	<1	5.15	<0.01	22.43	936	<2	0.01	1934	16	17	1	<0.01	19	<10	28
044197	<1	0.12	<10	5.4	<5	0.34	2	99	1059	5	5.16	<0.01	22.88	899	<2	0.01	2034	24	19	23	<0.01	19	<10	28
044198	<1	0.76	180	5.9	<5	0.83	2	99	2032	3	5.30	0.28	20.87	900	<2	0.24	2076	239	21	101	0.05	29	<10	41
044199	<1	0.08	<10	5.5	<5	0.92	2	101	1511	3	5.25	<0.01	22.23	842	<2	0.01	2128	34	17	19	<0.01	19	<10	31
044200	<1	0.05	11	6.1	<5	0.58	2	118	927	10	5.88	<0.01	22.51	748	<2	0.01	2342	45	25	18	<0.01	23	<10	31
Duplicates:																								
044101	<1	0.14	<10	5.3	<5	2.37	2	80	1291	2	5.02	0.01	16.79	489	<2	0.03	1774	22	19	34	<0.01	19	<10	29
044110	1	8.10	442	8.6	<5	3.12	7	42	75	48	7.64	1.25	3.41	3206	<2	2.76	34	863	984	450	0.48	255	<10	1205
044120	<1	0.12	<10	5.4	<5	1.25	2	99	1182	<1	5.27	<0.01	22.43	914	<2	0.01	1998	18	18	77	<0.01	15	10	55
044125	<1	0.08	15	6.3	<5	1.52	2	103	1814	<1	5.91	0.01	22.00	1190	<2	0.02	2267	19	23	63	<0.01	19	<10	66
044134	<1	0.08	29	6.2	<5	2.15	2	92	1279	<1	5.65	0.01	20.43	1059	<2	0.02	1963	63	15	377	<0.01	20	<10	47
044144	<1	0.16	13	5.6	<5	2.23	2	83	1468	4	5.24	0.01	21.14	1317	<2	0.02	1813	30	32	84	0.01	20	<10	56
044149	<1	7.96	180	7.7	<5	1.92	<1	53	352	<1	6.18	0.80	17.70	1159	<2	0.75	475	761	<2	85	0.34	197	<10	68
044158	<1	1.63	<10	6.0	<5	3.70	2	83	871	15	5.58	0.02	16.10	879	<2	0.06	1547	160	161	100	0.08	57	11	74
044168	<1	0.23	<10	7.1	<5	2.18	2	99	984	<1	6.26	0.01	21.89	1577	<2	0.03	2000	29	22	38	0.01	26	<10	62
044173	<1	0.06	<10	6.2	<5	0.14	2	108	900	<1	5.47	0.01	22.73	1243	<2	0.02	2159	24	21	4	<0.01	12	10	56
044182	<1	0.09	13	6.0	<5	0.94	2	106	1096	<1	5.72	0.01	24.97	1300	<2	0.02	2154	23	23	23	<0.01	21	<10	35
044192	<1	0.11	<10	5.9	<5	0.17	2	107	1494	<1	5.78	0.01	25.26	895	<2	0.02	2101	21	22	4	<0.01	20	<10	35
044197	<1	0.12	<10	5.5	<5	0.34	2	99	1207	<1	5.20	<0.01	22.99	908	<2	0.01	2042	21	19	24	<0.01	18	<10	31
Standards:																								
Blank	<1	0.01	<10	<0.5	<5	<0.01	<1	1	1	<1	0.02	<0.01	0.02	<5	<2	0.01	<1	<10	<2	<1	<0.01	<1	<10	<2
CH-4	2	7.54	475	6.5	<5	1.92	2	31	94	1962	5.58	1.81	1.43	458	<2	3.23	55	660	16	205	0.32	101	11	227

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2429RR

Date : Nov-24-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
044201	<1	0.11	12	5.6	<5	2.21	2	103	1284	2	5.11	0.01	22.71	898	<2	0.02	1944	32	23	191	<0.01	19	<10	50
044202	<1	0.11	21	5.4	<5	2.39	1	98	971	<1	5.04	0.01	21.14	999	4	0.02	1826	26	23	232	<0.01	19	<10	60
044203	<1	0.36	90	6.6	<5	0.99	2	108	1354	<1	6.14	0.14	23.94	793	2	0.07	2038	155	15	77	0.03	24	<10	41
044204	<1	0.05	<10	6.0	<5	1.08	2	109	821	<1	5.53	0.01	24.87	879	<2	0.01	2073	25	13	43	<0.01	16	<10	38
044205	<1	0.09	<10	5.9	<5	0.70	2	114	882	<1	5.61	0.02	26.86	863	2	0.01	2166	27	28	55	<0.01	16	<10	44
044206	<1	0.09	<10	5.6	<5	0.89	2	106	1200	<1	5.34	0.01	25.42	731	<2	0.01	1918	37	14	31	<0.01	16	<10	30
044207	<1	0.07	166	5.9	<5	2.18	2	107	1192	<1	5.55	0.01	24.12	799	<2	0.01	1911	12	32	141	<0.01	15	<10	39
044208	<1	0.08	19	7.1	<5	1.02	2	127	1594	<1	6.64	0.01	24.69	833	<2	0.01	2271	25	17	42	<0.01	16	<10	36
044209	<1	0.05	<10	7.5	<5	1.24	2	117	990	<1	6.99	<0.01	23.92	849	<2	0.01	2101	22	11	45	<0.01	18	<10	34
044210	<1	0.07	10	6.0	<5	1.15	2	94	953	<1	5.63	0.01	23.71	703	<2	0.01	1833	23	8	52	<0.01	16	<10	26
044211	<1	0.06	<10	6.8	<5	0.92	2	96	698	<1	6.23	<0.01	23.76	691	2	0.01	1921	14	11	72	<0.01	21	<10	31
044212	<1	0.09	<10	6.6	<5	0.61	2	96	1106	<1	6.08	<0.01	24.49	698	<2	0.01	1867	17	14	17	<0.01	17	<10	35
044213	<1	0.06	16	5.6	<5	1.72	2	108	1437	<1	5.15	<0.01	23.48	1065	<2	0.01	1912	25	17	131	<0.01	12	<10	43
044214	<1	7.34	2133	8.7	<5	5.24	1	46	253	21	6.40	4.08	4.40	1256	<2	1.71	50	3052	<2	1009	0.64	230	<10	86
044215	<1	6.27	1797	8.6	<5	5.82	1	56	338	17	6.45	3.00	7.52	1208	<2	1.37	335	2711	10	746	0.53	200	<10	85
044216	<1	0.09	17	6.2	<5	0.70	2	107	882	<1	6.16	0.04	25.18	956	<2	0.02	2050	47	16	21	0.01	18	<10	40
044217	<1	2.01	496	6.6	<5	2.16	2	96	651	12	5.81	0.65	20.12	1064	<2	0.50	1577	888	14	225	0.19	73	<10	44
044218	<1	0.06	10	6.9	<5	1.05	2	112	1449	<1	6.56	0.02	23.87	789	<2	0.01	2007	28	17	15	<0.01	13	<10	32
044219	<1	0.03	<10	6.6	<5	0.37	2	117	825	<1	6.41	0.01	25.40	796	<2	0.01	2203	21	10	7	<0.01	16	<10	30
044220	<1	0.03	<10	6.4	<5	1.06	2	115	979	<1	5.98	0.01	23.90	823	3	0.01	2096	17	16	26	<0.01	13	12	27
044221	<1	0.04	<10	6.3	<5	1.01	2	112	1265	<1	5.95	<0.01	23.96	853	<2	0.01	2104	27	13	17	<0.01	12	11	27
044222	<1	0.10	<10	6.3	<5	0.31	2	108	1883	<1	5.79	<0.01	24.67	832	<2	0.01	2001	18	12	5	<0.01	13	<10	30
044223	<1	0.10	81	6.4	<5	0.49	2	111	1638	<1	5.83	<0.01	24.73	861	<2	0.01	1990	25	23	8	<0.01	13	<10	33
044224	<1	0.08	<10	6.0	<5	0.89	2	108	1205	<1	5.64	<0.01	24.26	921	<2	0.01	1912	12	11	8	<0.01	15	<10	35
044225	<1	0.09	15	6.2	<5	0.73	2	114	1500	1	5.82	<0.01	24.77	750	<2	0.01	2228	26	14	6	<0.01	15	13	32
044226	<1	0.10	<10	6.1	<5	0.07	2	112	1195	8	5.89	<0.01	24.92	673	<2	0.01	2155	26	15	2	<0.01	17	18	30
044227	<1	0.16	<10	6.4	<5	0.19	2	112	1261	9	6.00	<0.01	25.61	840	<2	0.01	2133	46	15	16	<0.01	19	21	27
044228	<1	2.20	<10	6.9	<5	0.28	2	95	2400	16	6.42	0.02	23.58	1035	<2	0.01	1631	206	6	15	0.10	55	18	34
044229	<1	0.12	<10	7.0	<5	0.19	2	112	1946	19	6.59	<0.01	24.82	842	<2	0.01	2130	30	10	2	<0.01	16	<10	24
044230	1	0.12	<10	5.4	<5	0.87	2	106	1955	20	5.24	<0.01	24.08	806	<2	0.01	2000	22	13	6	<0.01	13	20	23

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2429RR

Date : Nov-24-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
044231	<1	0.12	<10	5.8	<5	1.25	2	108	1694	9	5.47	<0.01	24.31	1025	<2	0.01	1960	29	9	18	<0.01	14	17	22
044232	<1	0.14	<10	5.8	<5	0.88	1	117	2244	22	5.38	<0.01	24.58	729	3	0.01	2188	36	14	23	<0.01	15	14	30
044233	<1	0.18	<10	6.8	<5	0.43	2	113	2889	21	6.22	<0.01	24.08	664	2	0.01	2064	27	18	7	<0.01	16	21	32
044234	<1	0.10	<10	5.4	<5	0.16	1	132	1688	38	5.10	<0.01	25.28	845	7	0.01	2136	36	18	2	<0.01	14	12	21
044235	1	0.09	<10	5.8	<5	0.02	1	127	1081	33	5.37	<0.01	27.54	809	8	0.01	2394	32	15	1	<0.01	16	18	23
044236	1	0.08	<10	6.3	<5	0.01	2	117	865	18	5.93	<0.01	26.83	850	<2	0.01	2160	33	13	1	<0.01	18	14	21
044237	<1	0.08	<10	6.0	<5	0.01	2	112	1330	18	5.67	<0.01	26.12	712	<2	0.01	2128	19	12	1	<0.01	15	19	15
044238	1	0.13	<10	6.3	<5	0.02	2	115	1614	6	5.85	<0.01	26.49	718	<2	0.01	2208	39	15	1	<0.01	17	18	17
044239	1	0.10	<10	6.3	<5	0.06	2	129	1522	7	5.79	<0.01	27.46	759	<2	0.01	2399	36	21	2	<0.01	17	14	20
044240	<1	0.11	<10	6.2	<5	0.03	2	119	1170	5	5.87	<0.01	27.02	769	5	0.01	2261	25	15	1	<0.01	18	20	19
044241	<1	0.13	<10	5.7	<5	0.17	2	113	1318	5	5.41	<0.01	25.02	711	<2	0.01	2121	21	11	4	<0.01	17	10	16
044242	<1	0.17	<10	6.4	<5	0.61	2	110	1603	4	6.24	0.01	25.32	797	<2	0.01	2185	39	15	29	<0.01	20	10	25
044243	1	0.12	<10	5.9	<5	0.17	2	122	1843	10	5.71	<0.01	25.53	810	3	0.01	2425	31	15	3	<0.01	16	17	21
044244	<1	0.13	<10	6.5	<5	0.55	2	106	1968	2	5.91	<0.01	24.39	856	<2	0.01	2033	13	18	25	<0.01	16	14	26
044245	<1	0.10	<10	6.2	<5	0.02	2	108	1784	3	5.78	<0.01	26.17	815	<2	0.01	2154	25	13	1	<0.01	16	19	19
044246	<1	0.11	<10	6.4	<5	0.08	2	112	1030	1	5.82	<0.01	26.81	766	<2	0.01	2205	20	13	2	<0.01	18	18	18
044247	1	0.11	<10	6.7	<5	0.03	2	122	1439	3	6.27	<0.01	27.81	803	<2	0.01	2302	20	10	1	<0.01	19	16	20
044248	<1	0.11	<10	6.5	<5	0.03	2	133	1593	3	6.38	0.01	28.62	999	<2	0.01	2379	35	11	1	<0.01	18	15	24
044249	1	0.14	<10	6.3	<5	0.01	2	129	1932	<1	6.01	<0.01	26.58	825	<2	0.01	2292	23	12	1	<0.01	15	11	20
044250	<1	0.14	<10	6.1	<5	0.02	2	107	2240	<1	6.05	0.01	26.28	668	<2	0.01	2163	32	9	1	<0.01	15	<10	32
044251	<1	0.13	<10	6.1	<5	0.14	2	94	2067	<1	5.72	<0.01	24.88	670	<2	0.01	2050	20	14	2	<0.01	15	12	19
044252	<1	0.12	<10	5.8	<5	0.55	1	103	1671	<1	5.55	0.01	24.80	920	5	0.01	2034	26	15	24	<0.01	17	12	23
044253	<1	0.13	<10	5.4	<5	0.06	1	100	2054	<1	5.25	<0.01	25.27	782	<2	0.01	2044	30	15	3	<0.01	12	<10	31
044254	1	0.12	<10	6.2	<5	0.07	2	107	1842	<1	5.93	<0.01	25.89	1050	<2	0.01	2187	44	11	2	<0.01	16	<10	23
044255	<1	0.05	<10	5.1	<5	0.48	1	95	1156	<1	4.83	<0.01	21.57	751	<2	<0.01	1646	16	9	4	<0.01	14	<10	16
044256	<1	0.07	<10	6.5	<5	0.12	2	124	1437	<1	6.32	0.01	27.32	783	<2	0.01	2283	25	6	2	<0.01	16	<10	18
044257	<1	0.11	<10	6.6	<5	0.11	2	125	1871	<1	6.22	0.01	26.28	818	<2	0.01	2252	33	15	2	<0.01	17	<10	16
044258	<1	0.09	<10	6.0	<5	0.57	2	104	1596	<1	5.93	0.01	27.38	934	<2	0.01	2157	29	20	11	<0.01	16	<10	19
044259	1	0.09	<10	5.8	<5	0.34	2	105	1682	<1	5.62	<0.01	25.79	956	<2	0.01	2014	24	6	18	<0.01	15	11	26
044260	1	0.07	<10	5.6	<5	0.17	2	112	1429	<1	5.57	0.01	26.24	880	<2	0.01	2117	30	21	6	<0.01	15	12	21

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2429RR

Date : Nov-24-08

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
044261	<1	0.08	64	6.5	<5	0.09	2	117	1760	<1	6.26	<0.01	26.21	964	<2	0.01	2163	15	19	4	<0.01	16	11	23
044262	1	0.06	<10	6.3	<5	0.11	2	121	1265	<1	6.14	<0.01	25.70	905	<2	0.01	2120	30	12	5	<0.01	16	<10	28
044263	1	0.08	100	6.0	<5	0.27	2	115	1133	<1	5.90	0.01	24.98	864	<2	0.01	2188	20	29	15	<0.01	18	15	29
044264	<1	0.07	<10	5.9	<5	0.36	2	106	1085	<1	5.62	<0.01	24.24	811	<2	0.01	1994	26	11	23	<0.01	16	14	27
044265	1	0.16	11	5.8	<5	0.55	1	86	1609	<1	5.33	0.01	24.23	1055	<2	0.01	1883	23	13	16	<0.01	15	13	26
044266	<1	11.36	3159	5.6	<5	6.69	1	33	54	407	5.10	5.00	4.27	600	<2	0.45	54	1024	<2	1711	0.28	130	<10	18
044267	<1	0.71	17	5.9	<5	0.17	1	125	1520	57	5.31	0.02	23.79	766	<2	0.02	1922	85	13	7	0.02	19	<10	33
044268	<1	0.13	14	4.9	<5	0.13	1	146	1723	59	4.68	0.01	26.74	799	<2	0.02	2352	19	11	5	<0.01	13	13	30
044269	<1	0.10	10	4.6	<5	0.10	1	194	1884	63	4.39	<0.01	27.82	962	<2	0.01	2283	29	14	2	<0.01	12	10	34
044270	<1	0.14	<10	5.7	<5	0.05	2	150	2757	<1	5.37	<0.01	26.90	1017	<2	0.01	2260	19	11	2	<0.01	9	14	27
044271	<1	0.11	12	6.1	<5	0.35	2	131	2538	<1	5.83	<0.01	27.77	1031	<2	0.01	2248	36	19	3	<0.01	11	14	34
044272	<1	0.08	<10	6.5	<5	0.93	2	130	1744	<1	6.20	<0.01	26.59	935	<2	0.01	2130	29	17	5	<0.01	17	11	34
044273	1	0.07	<10	6.5	<5	0.90	2	121	2329	<1	5.98	<0.01	25.56	863	<2	0.01	2224	14	4	3	<0.01	12	12	28
044274	<1	0.09	<10	6.4	<5	0.45	1	121	1931	<1	5.94	<0.01	26.30	921	<2	0.02	2259	34	7	1	<0.01	15	10	31
044275	<1	0.10	<10	6.3	<5	0.02	1	128	2067	<1	5.76	<0.01	25.47	1009	<2	0.01	2232	22	13	1	<0.01	15	11	32
044276	1	0.13	<10	6.4	<5	0.13	2	120	2282	<1	5.90	<0.01	24.74	1010	<2	0.02	2089	26	3	2	<0.01	14	<10	35
044277	<1	0.16	<10	7.0	<5	0.03	2	118	4011	<1	6.48	0.01	25.02	1005	<2	0.02	2204	35	9	1	<0.01	13	15	42
044278	1	0.18	<10	7.0	<5	0.02	2	114	3885	<1	6.50	<0.01	24.50	915	<2	0.01	1972	26	8	1	<0.01	13	<10	45
044279	<1	0.33	65	6.5	<5	0.15	2	116	1708	<1	6.11	0.09	26.64	968	<2	0.07	2369	90	10	33	0.02	20	12	26
044280	<1	0.05	<10	5.9	<5	0.50	1	113	1308	<1	5.42	<0.01	25.48	1052	<2	0.01	2191	22	11	14	<0.01	14	<10	22
044281	<1	0.08	<10	5.7	<5	0.08	1	108	1440	<1	5.35	<0.01	26.02	913	<2	0.01	2025	20	13	3	<0.01	14	13	20
044282	<1	0.12	<10	6.0	<5	0.06	1	109	2101	<1	5.53	<0.01	26.08	852	<2	0.02	2106	11	7	6	<0.01	13	<10	19
044283	<1	0.09	<10	6.5	<5	0.39	2	108	2028	<1	6.12	<0.01	24.96	878	<2	0.01	2073	<10	3	15	<0.01	16	12	18
044284	1	0.10	<10	6.0	<5	0.24	1	113	1908	<1	5.71	0.01	26.94	908	<2	0.01	2286	17	3	9	<0.01	14	<10	21
044285	<1	0.12	<10	6.0	<5	0.31	1	107	2140	<1	5.73	0.01	24.37	858	<2	0.01	2018	24	22	11	<0.01	13	10	25
044286	<1	0.06	<10	6.0	<5	0.11	1	114	1344	<1	5.60	<0.01	26.24	919	<2	0.01	2195	11	9	4	<0.01	13	<10	19
044287	<1	0.05	<10	5.9	<5	0.09	1	116	1204	<1	5.53	<0.01	26.23	882	<2	0.01	2176	12	8	3	<0.01	13	<10	20
044288	<1	0.04	<10	6.1	<5	0.03	1	121	928	<1	5.77	<0.01	27.34	871	<2	0.01	2374	27	7	2	<0.01	15	<10	18
044289	1	0.07	<10	6.0	<5	0.12	1	113	1174	<1	5.81	<0.01	25.72	822	<2	0.01	2265	22	9	6	<0.01	16	<10	16
044290	1	0.08	<10	6.5	<5	0.16	2	121	1348	<1	6.19	0.01	26.78	886	<2	0.01	2436	30	8	8	<0.01	17	10	22

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2429RR

Date : Nov-24-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
044291	<1	0.10	<10	6.0	<5	0.11	1	116	1274	<1	5.63	0.01	26.49	818	<2	0.01	2245	21	11	6	<0.01	15	<10	19
044292	<1	0.05	<10	5.8	<5	0.06	1	125	1427	<1	5.56	<0.01	27.37	1042	<2	0.01	2366	30	5	3	<0.01	13	<10	20
044293	1	0.06	<10	6.6	<5	0.09	2	130	1658	<1	6.27	0.01	28.47	1110	<2	0.01	2506	19	11	3	<0.01	14	<10	23
044294	1	0.04	10	5.6	<5	0.66	1	112	907	<1	5.18	<0.01	25.47	942	<2	0.01	2125	11	9	35	<0.01	14	10	23
044295	<1	0.05	<10	6.2	<5	0.14	2	121	1337	<1	5.82	0.01	28.37	1022	<2	0.01	2470	29	13	4	<0.01	14	<10	19
044296	1	0.10	<10	5.8	<5	0.17	1	114	1837	<1	5.47	0.01	26.51	1101	<2	0.01	2288	15	8	4	<0.01	14	10	23
044297	<1	0.10	<10	6.5	<5	0.12	2	114	1787	<1	6.04	<0.01	26.85	1055	<2	0.01	2199	17	7	6	<0.01	16	<10	22
044298	<1	0.22	<10	6.6	<5	0.02	2	116	2152	<1	6.20	0.01	27.78	1141	<2	0.01	2282	24	<2	1	0.01	16	11	24
044299	<1	0.09	<10	5.9	<5	0.13	1	112	1518	<1	5.45	<0.01	25.96	964	<2	0.01	2238	22	5	6	<0.01	15	<10	18
044300	2	0.13	<10	6.5	<5	0.02	2	108	1967	<1	6.12	<0.01	26.16	872	<2	0.01	2256	14	9	1	<0.01	16	10	20
Duplicates:																								
044201	<1	0.11	12	5.4	<5	2.19	1	101	1417	<1	5.12	0.01	22.65	891	<2	0.02	1916	35	28	188	<0.01	19	<10	58
044210	<1	0.07	10	6.2	<5	1.16	1	95	982	<1	5.70	0.02	23.84	706	<2	0.01	1840	21	18	51	<0.01	15	10	32
044220	<1	0.03	<10	6.5	<5	1.05	2	115	913	<1	6.06	0.01	23.85	821	<2	0.01	2099	27	11	25	<0.01	15	<10	34
044225	<1	0.10	15	6.3	<5	0.74	2	118	1398	<1	5.94	0.01	25.48	766	<2	0.01	2270	26	11	6	<0.01	18	11	31
044234	<1	0.11	<10	5.8	<5	0.17	2	141	1426	37	5.34	<0.01	26.45	889	<2	0.01	2267	32	10	2	<0.01	17	19	26
044244	<1	0.13	<10	6.3	<5	0.55	2	106	1932	4	5.87	<0.01	24.34	852	<2	0.01	2043	31	15	26	<0.01	20	11	34
044249	<1	0.14	<10	6.3	<5	0.02	2	129	1782	<1	6.03	<0.01	26.56	828	<2	0.01	2295	12	11	1	<0.01	16	<10	19
044258	<1	0.09	<10	5.9	<5	0.53	2	98	1654	<1	5.59	<0.01	25.89	881	<2	0.01	2003	14	12	11	<0.01	16	11	17
044268	1	0.13	12	5.0	<5	0.13	1	148	1763	63	4.74	0.01	26.92	797	12	0.01	2398	23	12	5	<0.01	8	10	25
044273	<1	0.06	<10	6.4	<5	0.89	2	122	1921	<1	5.90	<0.01	25.56	854	<2	0.01	2232	13	7	2	<0.01	13	<10	24
044282	<1	0.12	<10	6.1	<5	0.06	1	107	2113	<1	5.51	<0.01	25.82	850	<2	0.01	2077	25	6	7	<0.01	13	<10	20
044292	<1	0.05	<10	6.0	<5	0.07	1	122	1347	<1	5.53	<0.01	27.42	1043	<2	0.01	2375	19	5	3	<0.01	12	10	19
044297	<1	0.09	<10	6.5	<5	0.12	2	113	1837	<1	6.21	<0.01	27.19	1066	<2	0.01	2180	21	18	6	<0.01	14	16	23
Standards:																								
Blank	<1	0.01	<10	<0.5	<5	0.01	<1	1	6	<1	0.03	<0.01	0.01	<5	<2	0.01	1	<10	<2	1	<0.01	<1	<10	<2
CH-4	2	7.90	496	7.0	<5	2.04	2	34	133	2087	5.76	1.89	1.55	484	<2	3.32	55	673	17	216	0.30	104	<10	233

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2488RR

Date : Nov-24-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
044301	<1	0.10	56	3.8	45	0.21	3	94	1855	7	6.38	0.02	28.03	1121	<2	0.02	2469	57	21	4	<0.01	10	<10	30
044302	<1	0.09	52	3.2	38	0.10	3	81	1279	4	5.71	0.02	26.34	886	<2	0.02	2337	37	19	4	<0.01	11	<10	22
044303	<1	0.13	52	3.3	37	0.03	3	79	1727	<1	5.76	0.02	26.76	767	<2	0.02	2370	33	17	2	<0.01	11	<10	21
044304	<1	0.10	66	3.1	44	0.03	3	84	1365	<1	5.31	0.02	27.73	724	<2	0.02	2528	55	20	1	<0.01	12	<10	19
044305	<1	0.12	81	3.3	52	0.04	3	80	1716	<1	5.79	0.02	27.49	702	<2	0.02	2389	35	16	2	<0.01	13	<10	19
044306	<1	0.17	92	3.5	44	0.05	3	72	1833	<1	6.08	0.02	26.72	807	<2	0.02	2280	59	19	2	<0.01	15	<10	19
044307	<1	0.12	77	2.9	47	1.26	2	61	1208	<1	5.03	0.02	24.59	939	<2	0.02	1915	38	16	86	<0.01	12	<10	33
044308	<1	0.10	57	3.1	45	0.26	2	75	1199	4	5.45	0.02	25.59	801	<2	0.02	2186	35	22	8	<0.01	12	<10	23
044309	<1	0.12	49	3.2	45	0.12	2	74	2129	9	5.53	0.01	25.86	938	<2	0.02	2121	39	17	3	<0.01	9	<10	24
044310	<1	0.60	126	3.4	30	1.68	2	67	1366	21	5.32	0.08	22.93	766	<2	0.03	1908	153	24	81	0.02	22	<10	37
044311	<1	7.82	2230	7.0	<5	5.53	2	38	747	40	6.71	4.08	8.40	1666	<2	1.14	330	2930	162	686	0.34	156	<10	186
044312	<1	7.50	1878	7.0	8	5.59	2	39	754	57	6.49	4.06	8.25	1151	<2	1.78	346	2865	43	727	0.33	155	<10	79
044313	<1	7.10	1733	6.7	7	5.66	2	38	818	56	6.32	3.82	8.20	1107	<2	1.77	347	2602	29	687	0.31	149	<10	72
044314	<1	7.26	1838	6.8	<5	5.78	2	38	805	49	6.54	3.93	8.57	1104	<2	1.86	351	2634	15	717	0.33	152	<10	70
044315	<1	7.10	1704	6.8	15	4.33	2	38	865	41	6.29	3.62	8.81	947	<2	1.65	351	2619	29	609	0.31	148	<10	70
044316	<1	6.99	1766	6.5	5	4.65	1	38	761	39	6.17	3.74	8.61	893	<2	1.60	349	2629	16	809	0.32	148	<10	59
044317	<1	7.08	1758	6.7	6	5.56	2	38	749	54	6.39	3.96	8.56	1051	<2	1.40	344	2766	16	647	0.32	148	<10	66
044318	<1	7.49	1748	6.6	<5	5.28	1	37	704	61	6.18	3.96	8.11	1043	<2	1.67	332	2672	19	724	0.32	150	<10	77
044319	<1	7.83	1751	6.8	6	3.12	1	42	830	<1	6.58	4.39	9.56	831	<2	1.25	346	2916	17	615	0.35	160	<10	65
044320	<1	7.57	1781	6.8	5	4.67	1	38	783	57	6.47	4.12	8.29	958	<2	1.66	327	2864	16	801	0.33	154	<10	63
044321	<1	7.34	1844	6.7	<5	4.62	1	36	764	61	6.19	3.96	7.88	931	<2	1.70	314	2702	26	738	0.32	151	<10	70
044322	<1	7.42	1736	6.8	<5	4.47	1	37	680	59	6.20	3.78	7.72	922	<2	1.65	307	2712	36	972	0.31	144	<10	66
044323	<1	7.69	1817	7.2	8	4.91	1	38	671	76	6.53	4.13	7.72	1084	<2	1.67	316	2717	32	943	0.32	149	<10	82
044324	<1	6.81	1631	6.5	9	5.46	1	36	771	51	6.09	3.75	7.83	1058	<2	1.55	337	2578	13	653	0.31	141	<10	71
044325	<1	6.79	1552	6.8	<5	5.91	2	41	900	54	6.78	3.59	9.22	1101	<2	1.47	384	2553	11	636	0.31	151	<10	73
044326	<1	7.01	1667	6.9	<5	6.14	2	39	878	62	6.60	3.74	8.81	1171	<2	1.53	352	2644	19	731	0.32	155	<10	74
044327	<1	7.14	1592	7.0	<5	6.05	2	39	929	53	6.51	3.68	8.69	1120	<2	1.72	345	2634	11	691	0.31	151	<10	71
044328	1	0.15	162	4.0	42	0.21	3	107	995	57	7.00	0.04	28.20	792	<2	0.03	2280	61	15	9	<0.01	17	<10	24
044329	<1	1.02	309	4.6	38	0.87	3	96	1737	51	7.13	0.50	26.33	892	<2	0.21	2052	435	16	86	0.05	35	<10	28
044330	<1	0.16	54	4.2	40	0.04	3	121	1686	25	7.11	0.02	30.06	849	<2	0.02	2385	18	18	3	<0.01	17	<10	18

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2488RR

Date : Nov-24-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
044331	<1	0.13	55	4.1	35	0.10	3	138	1907	34	6.87	0.02	30.87	873	<2	0.02	2496	51	16	2	<0.01	15	<10	19
044332	<1	0.15	56	3.4	36	0.05	3	118	2073	31	6.17	0.01	29.87	888	<2	0.02	2316	78	12	1	<0.01	15	<10	20
044333	<1	0.16	53	3.7	44	0.48	3	118	2199	35	6.55	0.02	28.77	981	<2	0.02	2234	51	18	11	<0.01	15	<10	22
044334	1	0.14	52	3.6	34	0.51	3	132	2439	53	6.54	0.01	27.98	834	<2	0.02	2340	39	18	6	<0.01	10	<10	37
044335	<1	0.67	188	3.6	30	0.48	2	112	1578	37	5.72	0.25	27.05	738	<2	0.16	1969	276	19	62	0.03	22	<10	33
044336	<1	7.04	1417	7.0	<5	5.59	2	43	841	39	6.61	3.14	10.70	1206	<2	1.67	540	2649	11	714	0.30	144	<10	93
044337	<1	6.43	1427	6.6	11	5.69	2	43	1069	50	6.83	3.55	11.25	1118	<2	1.23	479	2454	12	617	0.30	143	<10	79
044338	<1	0.10	55	3.6	38	0.52	3	138	1118	94	6.21	0.03	27.46	764	<2	0.02	2528	73	20	7	<0.01	13	<10	33
044339	<1	0.12	54	4.0	37	0.16	3	109	1921	50	7.13	0.02	28.78	973	<2	0.03	2367	81	15	3	<0.01	13	<10	27
044340	<1	0.12	52	3.9	35	0.16	3	88	2081	19	6.61	0.01	28.16	940	<2	0.02	2410	84	17	4	<0.01	13	<10	24
044341	<1	0.11	54	4.0	43	0.16	3	90	2649	15	7.07	0.02	29.26	924	<2	0.02	2454	39	19	2	<0.01	13	<10	27
044342	<1	0.12	52	3.6	39	0.14	3	81	1680	14	6.57	0.02	29.61	864	<2	0.02	2430	66	11	2	<0.01	14	<10	23
044343	<1	0.13	55	3.7	37	0.20	3	90	1867	13	6.50	0.02	29.81	883	<2	0.02	2418	66	18	3	<0.01	15	<10	36
044344	<1	0.12	52	3.7	37	0.16	3	98	1598	16	6.61	0.01	30.21	876	<2	0.02	2432	74	13	3	<0.01	14	<10	24
044345	<1	0.09	53	3.8	32	0.23	3	117	1613	22	6.74	0.02	30.01	925	<2	0.02	2575	74	20	6	<0.01	12	<10	28
044346	<1	0.07	51	4.3	39	0.15	3	123	2678	31	7.18	0.01	30.00	992	<2	0.02	2653	55	16	2	<0.01	8	<10	42
044347	<1	0.07	56	4.0	47	0.29	3	116	1447	26	6.70	0.02	29.80	993	<2	0.03	2602	51	16	8	<0.01	10	<10	32
044348	<1	6.66	1410	6.8	<5	5.78	2	40	874	34	6.54	3.20	10.06	1084	<2	1.19	447	2464	19	583	0.29	142	<10	74
044349	1	0.53	52	3.5	33	0.19	3	64	1577	9	5.73	0.02	25.66	973	<2	0.02	1874	45	17	7	0.01	19	<10	29
044350	<1	0.07	53	3.7	39	0.03	3	92	1448	<1	6.56	0.02	27.55	687	<2	0.02	2455	34	17	2	<0.01	11	<10	16
044351	<1	0.08	64	4.2	50	0.06	4	91	1940	<1	7.19	0.01	28.68	778	<2	0.02	2627	19	16	3	<0.01	10	<10	19
044352	1	0.10	50	3.9	36	0.21	3	84	2190	<1	6.68	0.01	27.85	918	<2	0.02	2724	35	18	4	<0.01	9	<10	19
044353	<1	0.10	60	4.2	46	1.40	4	85	2206	<1	7.20	0.01	29.06	1127	<2	0.02	2880	45	15	13	<0.01	11	<10	23
044354	<1	0.16	57	4.1	38	0.85	3	117	1678	15	6.97	0.01	25.03	855	<2	0.02	2178	41	23	27	0.01	17	<10	30
044355	<1	0.10	49	3.4	36	1.27	3	109	1887	6	6.06	0.01	24.79	1033	<2	0.01	2283	37	15	44	<0.01	13	<10	40
044356	<1	0.08	48	3.3	43	1.62	3	99	1706	<1	5.89	0.01	24.34	1173	<2	0.01	1900	51	19	85	<0.01	12	<10	44
044357	<1	0.09	50	3.1	31	1.34	3	92	1543	<1	5.51	0.01	24.69	1061	<2	0.01	2096	<10	18	69	<0.01	12	<10	34
044358	<1	0.07	47	3.3	33	2.11	3	71	1711	2	5.83	0.01	25.08	1421	<2	0.01	2151	53	15	76	<0.01	12	<10	44
044359	<1	0.07	49	3.8	43	0.47	3	64	1753	<1	6.57	0.01	27.04	1014	<2	0.02	2424	53	12	10	<0.01	13	<10	30
044360	<1	0.08	50	3.6	49	0.29	3	60	2267	<1	6.46	0.01	27.82	1242	<2	0.02	2448	60	15	8	<0.01	13	<10	41

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2488RR

Date : Nov-24-08

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
044361	<1	0.08	49	3.6	41	0.13	3	58	2091	<1	6.62	0.01	27.21	1103	<2	0.01	2450	48	16	3	<0.01	14	<10	37
044362	<1	0.07	47	3.8	40	0.17	3	56	1876	<1	6.50	0.01	26.23	956	<2	0.01	2366	46	12	7	<0.01	13	<10	32
044363	<1	0.06	50	3.8	37	0.38	4	60	1936	<1	6.58	0.01	25.95	939	<2	0.01	2432	42	8	16	<0.01	12	<10	32
044364	1	0.06	52	3.7	37	0.77	3	56	2010	<1	6.35	0.01	25.33	951	<2	0.01	2297	47	22	24	<0.01	11	<10	34
044365	<1	0.06	50	3.4	50	0.83	3	57	1981	<1	6.12	0.01	25.01	959	<2	0.01	2316	49	17	32	<0.01	12	<10	33
044366	<1	0.06	50	3.6	38	0.88	3	67	2087	<1	6.53	0.01	26.36	1001	<2	0.01	2427	54	18	25	<0.01	13	<10	34
044367	<1	0.06	50	3.7	43	0.72	3	72	1872	1	6.48	0.01	25.40	880	<2	0.01	2279	64	22	27	<0.01	12	<10	30
044368	<1	0.12	63	3.5	41	0.22	3	64	1897	<1	6.09	0.01	25.21	783	<2	0.01	2120	42	14	7	<0.01	11	<10	45
044369	<1	5.20	60	4.5	18	0.65	3	49	1072	2	7.45	0.10	22.27	1669	<2	0.23	1066	487	10	29	0.26	138	<10	59
044370	<1	1.88	53	3.4	32	0.44	3	53	1283	<1	5.86	0.01	27.15	1185	<2	0.02	1285	273	10	15	0.10	61	<10	28
044371	<1	0.20	50	3.4	32	0.29	3	62	1779	<1	6.05	0.01	25.80	910	<2	0.01	1991	43	16	6	0.01	13	<10	29
044372	1	0.09	48	4.1	37	0.08	3	70	1913	1	6.92	0.01	25.66	943	<2	0.01	2312	39	12	2	<0.01	13	<10	30
044373	<1	0.09	56	3.4	52	0.12	2	75	1464	11	5.95	0.01	25.88	773	<2	0.02	2064	15	14	3	<0.01	12	<10	22
044374	1	0.10	60	3.4	52	0.23	3	76	1645	10	6.09	0.01	26.51	955	<2	0.02	2151	53	18	3	<0.01	12	<10	28
044375	<1	0.09	58	3.4	49	0.18	3	74	1714	10	6.23	0.01	26.62	970	<2	0.01	2216	32	23	6	<0.01	11	<10	24
044376	<1	0.08	55	3.4	56	1.44	2	82	1563	11	6.12	0.01	25.33	1092	<2	0.01	2084	22	17	83	<0.01	11	<10	33
044377	1	0.08	56	3.2	48	0.79	2	80	1596	14	5.86	0.01	25.54	829	<2	0.01	1989	<10	22	31	<0.01	10	<10	33
044378	<1	0.05	62	3.4	47	1.00	3	68	1585	15	6.17	0.01	27.76	868	<2	0.02	2344	56	22	55	<0.01	9	<10	30
044379	<1	0.05	58	3.3	50	0.11	2	68	1565	11	5.78	0.01	27.03	778	<2	0.02	2280	31	13	2	<0.01	7	<10	23
044380	<1	0.09	59	3.3	65	0.39	2	77	2530	12	6.10	0.01	26.47	917	<2	0.01	2134	43	29	11	<0.01	6	<10	36
044381	<1	0.07	59	3.4	58	0.10	2	89	1920	15	6.10	0.01	27.23	818	<2	0.01	2223	49	12	1	<0.01	8	<10	31
044382	<1	0.08	91	3.4	57	0.21	2	84	1529	14	5.96	0.01	25.95	708	<2	0.01	2158	23	20	5	<0.01	10	<10	24
044383	<1	0.30	93	3.1	50	1.33	2	81	1483	7	5.29	0.01	24.49	778	<2	0.02	1949	33	11	33	<0.01	10	<10	25
044384	<1	11.31	2184	2.6	20	2.75	<1	4	57	66	3.94	3.49	13.87	1158	<2	0.85	46	1252	<2	828	0.21	115	<10	22
044385	<1	0.45	64	3.8	56	0.26	2	85	2037	2	6.41	0.02	25.14	828	<2	0.02	2240	54	16	9	0.01	11	<10	31
044386	<1	0.39	139	3.3	39	0.31	2	70	1453	<1	5.68	0.13	26.84	761	<2	0.02	1867	90	6	37	0.01	11	<10	23
044387	<1	0.10	59	3.3	44	0.18	2	62	1262	3	5.71	0.01	26.09	789	<2	0.02	2022	37	10	8	<0.01	8	<10	22
044388	<1	0.09	58	3.3	55	0.07	2	78	1642	6	6.00	0.01	26.96	746	<2	0.01	2068	30	12	2	<0.01	9	<10	25
044389	<1	0.09	60	3.6	46	0.04	3	82	2276	3	6.52	0.01	27.98	780	<2	0.01	2218	14	13	1	<0.01	8	<10	19
044390	<1	0.08	58	3.4	60	0.02	2	80	1625	<1	6.07	0.01	27.40	950	<2	0.01	2170	15	10	1	<0.01	9	<10	20

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

Assayers Canada
8282 Sherbrooke St., Vancouver, B.C., V5X 4R6
Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2488RR
Date : Nov-24-08

ICP-AES Report
Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
044391	<1	0.06	57	3.4	36	0.02	2	81	1309	<1	6.18	0.01	26.89	925	<2	0.01	2246	<10	15	1	<0.01	10	<10	27
044392	<1	0.22	59	3.6	43	0.04	2	84	1786	<1	6.42	0.01	26.67	873	<2	0.01	2237	36	11	1	0.01	14	<10	31
044393	<1	0.12	57	3.8	45	0.02	3	84	1876	<1	6.86	0.01	27.13	918	<2	0.01	2055	42	18	1	0.01	11	<10	28
044394	<1	0.97	57	3.4	39	0.08	2	71	1175	<1	5.95	0.01	26.07	803	<2	0.01	1891	51	8	2	0.06	31	<10	25
044395	<1	0.07	56	3.1	55	0.04	2	81	1001	<1	5.65	0.01	26.91	782	<2	0.01	2146	50	7	1	<0.01	10	<10	21
044396	<1	0.11	55	3.3	63	0.05	2	82	1125	<1	5.99	0.01	26.76	764	<2	0.01	2135	25	13	1	<0.01	13	<10	27
044397	<1	0.08	59	3.7	44	0.27	3	93	1800	24	6.46	0.02	27.86	1047	<2	0.01	2210	65	16	2	<0.01	10	<10	38
044398	<1	1.58	56	3.6	37	0.13	2	76	1714	7	6.42	0.01	26.73	1202	<2	0.01	1828	212	13	3	0.07	43	<10	38
044399	<1	0.09	55	3.4	49	0.03	2	85	1762	7	6.01	0.01	25.71	950	<2	0.01	2148	65	15	3	<0.01	9	<10	34
044400	<1	0.10	106	4.0	44	0.04	3	101	2106	4	6.95	0.01	25.27	1083	<2	0.01	2164	62	14	4	<0.01	14	<10	42
Duplicates:																								
044301	<1	0.09	77	3.6	44	0.20	2	93	1727	<1	6.13	0.03	27.02	1090	<2	0.02	2442	33	17	4	<0.01	10	<10	23
044310	1	0.61	64	3.4	40	1.65	2	68	1372	18	5.27	0.08	22.73	770	<2	0.03	1913	163	23	83	0.02	22	<10	36
044320	<1	7.33	1762	6.6	<5	4.45	1	37	717	49	6.18	3.99	7.92	922	<2	1.59	312	2760	15	776	0.32	149	<10	60
044325	<1	6.76	1534	6.9	<5	5.89	2	42	760	54	6.80	3.60	9.20	1102	<2	1.43	388	2704	13	638	0.31	151	<10	75
044334	<1	0.14	53	3.5	39	0.51	2	128	2356	50	6.42	0.02	27.31	820	<2	0.02	2281	75	14	6	<0.01	10	<10	34
044344	<1	0.12	54	3.7	38	0.16	3	96	1447	14	6.46	0.01	29.66	858	<2	0.02	2380	65	19	3	<0.01	14	<10	24
044349	<1	0.52	50	3.3	42	0.18	2	63	1719	7	5.48	0.02	24.45	938	<2	0.02	1777	62	16	7	0.01	18	<10	27
044358	<1	0.07	46	3.2	34	2.04	3	71	1690	2	5.63	0.01	24.42	1381	<2	0.01	2126	48	16	76	<0.01	11	<10	42
044368	<1	0.12	62	3.4	41	0.23	3	64	1958	<1	6.06	0.01	25.23	791	<2	0.01	2130	25	14	8	<0.01	10	<10	44
044373	<1	0.09	56	3.4	53	0.12	2	76	1687	13	6.13	0.01	26.55	790	<2	0.02	2064	36	12	3	<0.01	13	<10	25
044382	<1	0.08	95	3.4	42	0.21	3	87	1699	13	6.12	0.01	26.37	729	<2	0.02	2231	50	19	5	<0.01	11	<10	26
044392	<1	0.22	55	3.6	55	0.04	2	84	1971	<1	6.40	0.01	26.31	872	<2	0.01	2250	36	7	1	0.01	14	<10	31
044397	<1	0.07	56	3.5	46	0.25	2	92	1858	12	6.28	0.01	27.16	1017	<2	0.02	2185	100	15	2	<0.01	10	<10	41
Standards:																								
Blank	<1	0.01	<10	<0.5	<5	0.01	1	1	5	<1	0.02	<0.01	0.02	<5	<2	<0.01	1	<10	<2	<1	<0.01	<1	<10	<2
CH-4	2	7.71	487	4.2	<5	2.01	3	27	163	2028	6.03	1.82	1.39	474	<2	3.08	53	671	17	215	0.30	100	<10	223

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2537RR

Date : Nov-25-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
44401	1	1.58	78	4.5	43	0.61	3	102	1120	29	7.43	0.02	23.42	1244	<2	0.02	2070	208	21	7	0.07	49	<10	54
44402	<1	0.39	125	4.6	42	2.10	3	97	1307	19	6.77	0.01	22.50	1335	<2	0.02	2209	81	25	12	0.01	24	<10	61
44403	<1	6.05	234	4.4	18	4.67	2	42	522	10	6.72	0.92	13.24	1197	<2	0.56	714	722	9	690	0.27	158	<10	39
44404	<1	10.31	753	4.5	<5	6.29	1	28	61	39	6.99	2.83	3.84	929	<2	2.10	31	1089	<2	1260	0.46	235	<10	30
44405	<1	7.33	371	4.7	<5	3.42	2	42	648	18	7.00	0.94	12.62	1337	<2	1.60	640	794	12	442	0.35	174	<10	52
44406	<1	6.78	104	4.3	25	2.19	2	35	280	25	7.06	0.13	18.16	1908	<2	0.06	531	752	6	64	0.36	193	<10	55
44407	<1	5.03	662	5.1	17	5.17	2	51	641	114	6.61	0.95	13.46	1355	<2	0.56	932	1303	50	665	0.27	133	<10	107
44408	<1	1.40	65	3.5	39	1.09	2	79	932	33	5.79	0.03	24.04	914	<2	0.02	1726	155	16	71	0.08	49	<10	38
44409	<1	1.96	76	3.3	24	1.25	2	63	522	11	5.41	0.01	24.87	1059	<2	0.01	1417	244	12	159	0.12	66	<10	28
44410	<1	5.93	59	3.6	18	1.71	2	24	264	8	6.05	0.01	21.74	1396	<2	0.01	452	684	7	149	0.36	165	<10	38
44411	<1	4.57	57	3.8	16	0.62	2	49	419	24	6.20	0.01	22.72	1398	<2	0.01	1007	508	9	34	0.26	150	<10	36
44412	<1	1.24	54	3.5	43	0.48	2	74	823	12	5.82	<0.01	24.35	1115	<2	0.02	1842	176	15	29	0.07	47	<10	28
44413	<1	0.42	53	3.6	50	0.87	2	84	1373	15	5.82	<0.01	25.62	902	<2	0.02	1947	79	16	28	0.02	24	<10	43
44416	<1	0.50	52	3.3	40	0.87	2	90	1160	26	5.57	<0.01	24.93	906	<2	0.02	2084	81	21	25	0.02	24	<10	49
44417	<1	0.73	55	3.4	41	0.44	2	68	1841	17	5.77	<0.01	25.21	849	<2	0.02	1982	64	20	13	0.04	28	<10	31
44418	1	0.18	59	3.8	40	0.42	2	87	1985	8	5.64	<0.01	26.71	762	<2	0.02	2200	48	20	16	<0.01	16	<10	37
44419	<1	0.13	50	3.2	46	1.56	2	75	1368	9	5.02	<0.01	22.31	611	<2	0.03	1885	52	24	66	<0.01	16	<10	42
44420	<1	2.34	48	4.0	28	3.32	2	74	1518	23	6.11	0.01	18.32	1796	<2	0.04	1456	268	61	68	0.10	58	<10	159
44421	<1	0.09	54	4.1	43	1.23	2	72	1031	14	6.08	0.01	24.71	704	<2	0.02	2063	23	22	42	<0.01	17	<10	35
44422	<1	1.23	52	4.4	36	2.05	3	108	1493	24	6.91	0.03	21.39	1093	<2	0.04	2064	116	58	38	0.05	44	<10	109
44429	<1	0.19	65	3.3	38	0.44	2	86	1555	4	5.79	0.02	25.95	844	<2	0.03	2054	66	24	24	0.01	15	<10	36
44430	<1	1.04	85	3.8	47	0.67	3	76	2018	9	6.32	0.18	23.60	614	<2	0.42	1653	133	52	75	0.04	34	<10	76
44431	<1	0.23	54	3.5	44	0.34	2	74	2973	1	6.24	<0.01	26.09	698	<2	0.01	1621	44	38	20	<0.01	16	<10	34
44432	<1	0.17	54	3.2	47	0.53	2	81	2538	5	5.64	<0.01	25.53	1151	<2	0.01	2144	37	27	28	<0.01	11	<10	50
44433	<1	0.13	73	6.4	<5	0.74	2	110	1680	<1	5.27	0.01	24.83	1117	<2	0.02	2102	31	45	37	<0.01	15	10	50
44434	<1	0.20	29	6.5	<5	0.40	2	107	2070	<1	5.38	0.01	24.75	899	<2	0.02	2077	25	24	23	<0.01	17	<10	45
44435	<1	0.17	12	6.7	<5	0.55	2	108	2108	<1	5.53	0.01	25.15	861	<2	0.02	2025	20	64	26	<0.01	17	<10	34
44436	<1	0.13	<10	6.7	<5	0.31	2	112	1772	<1	5.68	<0.01	24.45	888	<2	0.04	2105	72	6	19	<0.01	18	<10	27
44437	<1	0.13	<10	6.9	<5	0.32	2	117	1677	<1	5.80	<0.01	25.67	887	<2	0.02	2189	26	8	15	<0.01	18	11	25
44438	<1	0.13	27	7.1	<5	0.26	2	117	2042	<1	5.92	<0.01	25.17	966	<2	0.02	2187	29	6	13	<0.01	14	10	25

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2537RR

Date : Nov-25-08

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
44439	<1	0.12	<10	6.6	<5	0.88	2	111	1242	<1	5.53	<0.01	25.02	1089	<2	0.02	2019	32	12	52	<0.01	18	<10	42
44440	<1	0.13	77	7.1	<5	0.48	2	123	1495	<1	5.98	0.01	27.30	1041	<2	0.02	2311	32	21	24	<0.01	17	<10	55
44441	<1	0.06	<10	7.0	<5	0.81	2	112	1609	<1	5.83	<0.01	25.03	1034	<2	0.02	2137	10	10	77	<0.01	13	10	35
44442	<1	0.13	67	6.9	<5	0.36	2	111	1965	<1	5.62	<0.01	25.63	964	<2	0.01	2106	23	10	22	<0.01	15	<10	35
44443	<1	0.09	30	7.6	<5	0.32	2	116	2086	<1	6.20	<0.01	25.33	1234	<2	0.01	2063	20	9	18	<0.01	12	<10	26
44444	<1	0.10	67	7.3	<5	0.87	2	112	2168	<1	6.03	<0.01	23.50	1088	<2	0.01	1996	27	21	74	<0.01	13	<10	64
44445	<1	0.11	85	7.5	<5	0.28	2	114	2085	<1	6.18	<0.01	25.16	942	<2	0.01	2123	19	10	17	<0.01	14	<10	29
44446	<1	0.12	<10	7.4	<5	0.30	2	116	2134	<1	6.27	<0.01	26.52	1073	<2	0.01	2129	25	10	12	<0.01	16	10	33
44447	<1	0.11	30	7.6	<5	0.07	2	123	1912	<1	6.31	<0.01	27.02	1095	<2	0.01	2337	27	13	3	<0.01	16	10	39
44448	<1	0.10	144	7.6	<5	0.10	2	116	2108	<1	6.23	<0.01	25.15	1138	<2	0.01	2360	16	6	4	<0.01	14	<10	28
44449	<1	0.10	136	7.4	<5	0.25	2	114	2089	<1	6.00	<0.01	25.04	1216	<2	0.01	2158	21	16	10	<0.01	12	<10	49
44450	<1	0.11	<10	6.9	<5	0.34	2	110	1811	<1	5.76	<0.01	25.55	1052	<2	0.01	2030	20	8	6	<0.01	14	10	30
44451	<1	0.10	104	7.4	<5	0.17	2	113	1837	<1	6.06	<0.01	25.67	1067	<2	0.01	2119	26	17	6	<0.01	14	<10	52
44452	<1	0.11	76	7.0	<5	0.24	2	114	1505	<1	5.83	<0.01	25.63	1039	<2	0.01	2137	23	11	11	<0.01	15	<10	40
44453	<1	0.09	75	6.7	<5	2.46	2	101	1948	<1	5.44	<0.01	24.99	1329	<2	0.01	1886	20	13	117	<0.01	13	<10	45
44454	<1	0.12	47	7.3	<5	0.58	2	121	2106	<1	6.15	<0.01	26.11	1286	<2	0.01	2242	24	18	27	<0.01	16	<10	54
44455	<1	0.15	90	7.1	<5	0.62	2	110	1653	<1	5.90	<0.01	24.94	1088	<2	0.01	1985	29	24	12	<0.01	16	<10	74
44456	<1	0.11	104	7.3	<5	0.54	2	122	1784	<1	6.16	<0.01	25.90	977	<2	0.01	2319	25	20	20	<0.01	17	<10	51
44457	<1	0.09	56	3.7	53	0.47	3	81	1359	5	6.56	0.01	26.09	941	<2	0.01	2108	13	25	7	<0.01	14	<10	33
44458	1	0.16	57	3.6	45	0.35	2	80	1540	9	6.22	0.01	26.03	960	<2	0.02	2286	42	14	10	0.01	17	<10	34
44460	<1	0.33	56	3.6	37	2.33	5	67	1848	14	5.84	0.01	22.65	1032	<2	0.01	1901	37	198	143	0.01	24	<10	107
44461	<1	0.05	58	3.6	51	0.46	3	79	1243	5	5.94	0.01	27.60	848	<2	0.01	2222	11	18	29	<0.01	11	<10	29
44462	1	0.06	66	3.3	45	0.54	3	86	1472	<1	6.03	0.01	26.19	801	<2	0.05	2170	129	19	11	<0.01	7	<10	32
44463	1	0.06	94	3.8	53	0.68	3	89	2034	<1	6.61	0.01	28.14	977	<2	0.01	2238	20	20	12	<0.01	7	<10	42
44464	<1	0.08	101	3.5	54	0.19	2	87	1046	<1	6.12	0.01	28.16	738	<2	0.02	2229	15	20	6	<0.01	12	<10	33
44465	<1	0.08	59	3.3	53	0.36	2	82	1417	<1	5.79	0.01	26.35	817	<2	0.01	2061	<10	22	16	<0.01	10	<10	35
44466	<1	0.09	62	3.4	37	0.53	2	82	1302	4	5.99	0.01	26.02	1000	<2	0.01	2095	13	17	32	<0.01	12	<10	44
44467	<1	0.07	55	3.0	49	1.05	2	67	1486	5	5.24	0.01	22.17	943	<2	0.02	1751	<10	19	70	<0.01	10	<10	55
44468	<1	0.07	59	3.7	39	0.43	3	90	1539	8	6.76	0.01	27.07	942	<2	0.02	2216	<10	27	12	<0.01	10	<10	38
44469	<1	0.13	60	3.3	43	0.88	2	75	1933	3	5.93	0.02	26.45	907	<2	0.02	1877	14	20	32	<0.01	10	<10	40

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2537RR

Date : Nov-25-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
44470	<1	0.11	58	3.2	51	0.67	2	72	1582	<1	5.61	0.01	26.29	832	<2	0.01	1859	16	17	14	<0.01	11	<10	36
44471	<1	0.10	60	3.6	39	0.07	2	84	1615	<1	6.42	0.01	27.44	866	<2	0.01	2242	26	20	2	<0.01	11	<10	30
44472	<1	0.10	58	3.3	39	0.10	2	82	1384	1	5.87	0.01	26.86	729	<2	0.01	2145	38	15	2	<0.01	11	<10	26
44473	<1	0.05	60	3.5	40	0.13	2	90	1363	<1	6.29	0.01	27.82	925	<2	0.01	2203	<10	24	3	<0.01	8	<10	26
44474	<1	0.05	61	3.6	50	0.13	3	86	1697	8	6.54	0.01	28.16	971	<2	0.01	2198	<10	29	3	<0.01	8	<10	33
44475	<1	0.08	58	3.4	50	0.14	2	82	972	8	6.09	0.01	27.13	795	<2	0.01	2156	20	21	4	<0.01	12	<10	31
44476	<1	0.07	58	3.4	56	0.33	3	86	1785	1	6.22	0.01	27.55	1002	<2	0.01	2256	43	19	11	<0.01	10	<10	30
44477	<1	0.05	57	3.3	46	0.20	3	85	1558	<1	6.10	0.01	27.66	1025	<2	0.01	2204	15	28	8	<0.01	9	<10	31
44478	<1	0.09	58	3.5	51	0.48	3	84	1779	<1	6.23	0.01	27.82	1010	<2	0.01	2263	<10	25	13	<0.01	11	<10	35
44479	<1	0.10	59	3.4	48	0.54	2	83	1654	1	6.12	0.01	26.60	952	<2	0.05	2237	122	89	13	<0.01	12	<10	33
44480	1	0.08	56	3.7	50	0.56	3	87	2717	1	6.57	0.01	26.35	1054	<2	0.01	2258	10	234	12	<0.01	7	<10	47
44481	<1	0.07	60	3.3	34	1.92	2	72	1844	3	5.99	0.01	26.50	1111	<2	0.01	2013	33	65	70	<0.01	8	<10	37
44482	<1	0.09	60	3.6	39	0.76	3	91	2556	11	6.38	0.02	27.78	1149	<2	0.01	2283	55	24	25	<0.01	6	<10	44
44483	<1	0.07	53	3.5	50	0.64	2	86	2516	9	6.33	0.01	25.07	980	<2	0.01	2229	62	17	38	<0.01	7	<10	37
44484	<1	0.09	52	3.7	43	0.62	2	73	2677	11	6.33	0.01	24.54	1158	<2	0.02	2216	43	16	50	<0.01	9	<10	46
44485	<1	0.09	52	3.8	49	1.15	2	68	2327	7	6.34	0.01	24.40	1182	<2	0.02	2087	55	18	84	<0.01	13	<10	49
44486	<1	2.32	52	3.7	39	1.51	2	51	1879	13	6.00	0.01	23.22	1614	<2	0.01	1466	259	10	63	0.10	53	<10	100
44487	<1	0.84	50	3.3	38	2.63	2	55	1774	11	5.45	0.01	21.96	1338	<2	0.02	1852	106	20	184	0.03	26	<10	84
44488	<1	0.10	52	3.5	46	0.33	2	58	2160	18	5.66	0.01	25.13	937	<2	0.01	1928	74	24	12	<0.01	12	<10	40
44489	<1	0.06	53	2.7	30	1.69	2	52	1644	23	4.85	0.01	25.30	1068	<2	0.01	1738	43	6	20	<0.01	8	<10	42
44490	1	0.68	244	2.9	39	4.15	3	35	2150	46	4.59	0.22	20.29	1382	<2	0.08	1198	136	263	166	0.03	18	<10	162
44491	<1	0.71	46	3.2	27	5.49	3	53	1313	56	5.29	0.01	16.78	935	<2	0.03	1550	94	141	267	0.03	26	<10	128
44492	<1	5.12	170	4.3	16	5.68	2	34	1074	24	6.25	0.60	15.13	1912	<2	0.34	958	628	123	195	0.22	119	<10	185
44493	<1	8.81	489	4.6	6	1.19	1	21	213	23	6.42	1.60	9.56	784	3	2.09	274	921	42	300	0.41	239	<10	85
44496	<1	0.20	54	3.6	49	1.89	2	71	2416	21	6.00	0.03	22.13	1179	<2	0.04	1894	74	28	57	0.01	12	<10	58
44497	<1	2.82	200	3.8	24	1.36	2	58	1325	18	5.73	0.53	19.07	1036	<2	0.79	1453	313	27	128	0.12	78	<10	57
44498	<1	9.38	360	4.5	6	3.60	1	23	155	18	7.09	1.60	12.16	1989	<2	1.08	167	1073	29	630	0.43	211	<10	153
44499	<1	9.87	363	4.2	<5	4.56	1	14	50	9	6.69	1.47	11.74	1623	<2	0.90	45	1066	7	653	0.43	209	<10	86
Duplicates:																								
44401	<1	1.63	76	4.6	47	0.63	3	104	1918	31	7.61	0.02	24.22	1278	<2	0.02	2159	229	28	8	0.07	49	<10	49

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2537RR

Date : Nov-25-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
44410	<1	6.28	60	3.9	<5	1.79	2	28	530	5	6.48	0.01	23.01	1485	<2	0.01	495	697	9	156	0.38	174	<10	40
44422	<1	1.18	51	4.2	42	1.96	3	101	1337	26	6.62	0.02	20.40	1037	<2	0.04	1967	127	61	37	0.05	42	<10	102
44433	<1	0.13	78	6.4	<5	0.74	2	109	1582	<1	5.29	<0.01	24.85	1117	<2	0.01	2109	26	46	37	<0.01	15	<10	47
44442	<1	0.13	11	6.8	<5	0.36	2	110	2127	<1	5.60	<0.01	25.57	967	<2	0.01	2135	21	12	21	<0.01	15	14	35
44452	<1	0.11	72	7.0	<5	0.25	2	114	1627	<1	5.82	<0.01	25.75	1046	<2	0.01	2132	21	16	12	<0.01	15	12	42
44457	<1	0.10	56	3.7	53	0.52	3	85	1496	4	6.64	0.01	26.70	972	<2	0.02	2168	<10	19	10	<0.01	14	<10	38
44467	<1	0.07	55	3.0	43	1.06	2	66	1420	7	5.27	0.01	22.46	946	<2	0.02	1762	<10	18	71	<0.01	10	<10	53
44477	<1	0.05	58	3.5	40	0.21	3	85	1650	3	6.24	0.01	28.18	1048	<2	0.01	2218	<10	20	8	<0.01	9	<10	36
44482	<1	0.09	59	3.3	46	0.71	2	86	2383	9	6.00	0.02	26.42	1089	<2	0.01	2181	25	26	23	<0.01	6	<10	40
44491	<1	0.70	47	3.1	24	5.49	3	53	1250	59	5.30	0.01	16.67	924	<2	0.03	1547	96	162	267	0.03	26	<10	137
Standards:																								
Blank	<1	0.01	<10	<0.5	<5	0.01	<1	1	4	1	<0.01	<0.01	0.01	<5	<2	<0.01	<1	<10	<2	<1	<0.01	<1	<10	<2
CH-4	2	7.65	486	4.0	<5	2.02	3	27	133	1995	5.79	1.83	1.44	476	<2	3.09	59	664	17	209	0.30	100	<10	228

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2560RR

Date : Nov-25-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
44503	<1	0.22	156	6.0	<5	1.15	2	97	1595	3	5.21	0.04	19.61	672	<2	0.04	2107	27	43	33	<0.01	19	<10	79
44504	<1	0.21	22	5.8	<5	0.78	2	99	1500	<1	5.18	0.03	20.53	708	<2	0.03	2136	11	18	20	<0.01	23	<10	39
44505	2	0.16	36	6.0	<5	0.45	2	110	2224	<1	5.52	0.02	22.35	1008	<2	0.02	2311	17	16	8	<0.01	19	<10	48
44506	<1	0.18	<10	5.8	<5	0.53	2	107	1489	<1	5.23	0.01	22.21	807	<2	0.02	2256	15	12	11	<0.01	24	<10	35
44509	<1	1.52	200	7.2	<5	2.59	2	96	1226	<1	5.97	0.37	17.15	1416	<2	0.53	1834	179	14	75	0.06	45	<10	82
44510	<1	5.88	182	7.6	<5	1.84	2	60	562	<1	6.82	0.39	14.72	1888	<2	0.47	828	657	10	87	0.25	148	<10	150
44511	<1	9.32	902	7.1	<5	1.40	1	48	203	48	5.90	1.80	6.68	1982	<2	3.63	272	1044	41	309	0.40	205	<10	176
44512	<1	1.19	68	4.9	<5	2.69	1	70	761	7	4.34	0.13	15.79	812	<2	0.39	1309	144	28	52	0.05	42	<10	58
44513	<1	0.32	25	6.7	<5	3.20	2	110	1142	5	5.75	0.03	20.69	1057	<2	0.05	1989	47	22	47	0.01	29	<10	55
44514	<1	0.12	11	6.3	<5	2.58	2	105	1284	<1	5.44	0.01	21.04	1325	<2	0.02	2243	17	12	34	<0.01	21	<10	50
44515	<1	1.14	11	6.9	<5	2.41	2	102	1683	<1	5.96	0.01	20.83	971	<2	0.03	2136	73	12	40	0.03	25	<10	42
44516	<1	0.07	<10	5.6	<5	1.48	1	113	744	<1	5.12	0.01	25.01	955	<2	0.02	2519	15	13	28	<0.01	14	<10	31
44517	1	0.07	<10	6.3	<5	0.63	2	118	1287	<1	6.03	0.01	25.00	1021	<2	0.01	2574	19	15	38	<0.01	15	<10	48
44518	<1	0.11	<10	5.6	<5	0.53	1	108	1167	<1	5.22	0.01	24.78	931	<2	0.01	2271	25	15	17	<0.01	15	10	38
44519	<1	0.06	<10	5.6	<5	0.33	1	110	1251	<1	5.44	<0.01	25.17	1076	<2	0.01	2380	14	11	21	<0.01	12	11	39
44520	<1	0.13	18	6.1	<5	0.10	2	106	1032	<1	5.77	<0.01	24.81	786	<2	0.01	2185	17	12	10	<0.01	17	<10	40
44521	<1	0.14	<10	5.8	<5	0.09	2	109	976	<1	5.48	0.01	24.73	719	<2	0.01	2307	15	9	7	<0.01	19	<10	39
44522	<1	0.12	<10	5.7	<5	0.09	2	110	831	<1	5.55	0.01	24.92	688	<2	0.01	2303	10	10	9	<0.01	18	11	37
44523	<1	0.12	<10	5.9	<5	0.09	2	113	905	<1	5.64	0.01	25.29	770	<2	0.01	2395	11	14	9	<0.01	19	10	40
44524	<1	0.14	<10	6.3	<5	0.32	2	113	1998	<1	5.95	<0.01	23.74	1070	<2	0.01	2280	15	16	10	<0.01	21	<10	58
44525	1	0.15	<10	6.1	<5	0.41	2	110	1252	<1	5.73	0.01	24.64	882	<2	0.01	2258	23	10	6	<0.01	21	<10	40
44526	<1	0.10	<10	3.9	<5	0.04	<1	<1	117	<1	5.30	0.10	23.29	801	<2	0.01	333	82	33	<1	<0.01	3	<10	9
44527	<1	2.09	12	5.1	<5	0.77	1	80	689	<1	4.63	0.01	22.38	1348	<2	0.01	1567	166	11	60	0.06	39	<10	76
44528	<1	0.33	<10	5.4	<5	1.13	1	101	957	<1	5.11	0.01	22.83	841	<2	0.01	2096	29	9	52	0.01	20	<10	40
44529	1	0.12	<10	5.4	<5	0.96	1	108	1003	<1	5.15	0.01	23.15	921	<2	0.02	2185	14	15	43	<0.01	18	<10	35
44530	1	0.12	<10	5.2	<5	1.29	2	99	714	<1	4.71	0.01	21.26	1040	<2	0.02	1956	13	14	71	<0.01	17	<10	91
44531	<1	0.11	<10	5.0	<5	0.55	1	88	803	<1	4.54	0.01	21.24	817	<2	0.02	1941	13	13	37	<0.01	17	<10	71
44532	2	0.23	<10	6.1	<5	0.60	2	102	1235	<1	5.68	0.01	22.22	1003	<2	0.02	2227	33	14	46	0.01	24	<10	61
44533	<1	0.10	<10	5.7	<5	0.59	2	109	1028	<1	5.40	<0.01	23.71	930	<2	0.01	2259	<10	18	20	<0.01	18	<10	32
44534	1	0.09	<10	5.9	<5	0.37	2	114	1262	<1	5.61	0.01	24.40	944	<2	0.01	2362	20	13	18	<0.01	16	<10	32

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2560RR

Date : Nov-25-08

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
44535	1	0.11	<10	6.0	<5	0.24	2	117	1283	<1	5.70	0.01	24.79	839	<2	0.01	2302	21	16	6	<0.01	17	<10	27
44536	1	0.14	<10	6.0	<5	1.13	2	115	1708	<1	5.64	0.01	24.03	986	<2	0.01	2275	23	14	57	<0.01	17	<10	43
44537	1	0.05	<10	5.4	<5	1.40	2	108	1285	<1	5.16	0.01	22.62	1318	<2	0.01	2215	18	14	275	<0.01	12	<10	42
44538	1	0.07	<10	5.5	<5	0.41	2	113	1210	<1	5.32	0.01	23.61	665	<2	0.01	2259	13	12	21	<0.01	14	<10	37
44539	1	0.09	<10	5.6	<5	0.34	2	112	1235	<1	5.31	0.01	23.73	707	<2	0.01	2239	16	16	6	<0.01	13	<10	34
44540	<1	0.08	<10	5.4	<5	0.70	2	109	703	<1	5.16	0.01	23.76	841	<2	0.01	2186	15	12	7	<0.01	15	<10	30
44541	<1	0.06	<10	5.9	<5	0.10	2	127	811	<1	5.76	0.01	24.80	871	<2	0.01	2576	17	12	4	<0.01	14	<10	30
44542	<1	0.06	<10	5.7	<5	0.19	2	118	845	<1	5.49	0.01	24.96	889	<2	0.01	2392	15	12	6	<0.01	14	10	34
44543	1	0.09	<10	5.9	<5	0.30	2	118	982	<1	5.68	0.01	25.57	876	<2	0.01	2491	12	14	7	<0.01	15	<10	33
44544	1	0.09	<10	6.1	<5	0.22	2	124	1669	<1	5.90	0.01	26.41	1056	<2	0.01	2679	20	14	5	<0.01	12	<10	47
44545	<1	0.08	<10	6.3	<5	0.19	2	115	1680	<1	5.92	0.01	23.69	825	<2	0.02	2359	16	14	3	<0.01	12	<10	43
44546	<1	0.08	<10	5.9	<5	0.12	2	102	1307	<1	5.36	0.01	23.60	883	<2	0.02	2475	16	13	3	<0.01	16	<10	43
44547	1	2.44	<10	6.7	<5	0.32	2	97	914	<1	6.30	0.01	21.05	962	<2	0.02	2020	193	6	22	0.11	80	<10	43
44548	1	0.09	<10	5.8	<5	0.04	2	115	1257	<1	5.31	0.01	24.32	763	<2	0.02	2237	13	11	3	<0.01	16	<10	33
44549	1	0.08	<10	5.9	<5	0.20	2	104	1444	<1	5.59	0.01	24.38	773	<2	0.02	2265	18	13	3	<0.01	12	<10	32
44550	<1	0.05	<10	5.5	<5	0.07	1	104	917	<1	5.14	0.01	23.96	641	<2	0.02	2382	22	14	3	<0.01	12	<10	33
44551	1	0.07	<10	6.3	<5	0.48	2	116	1183	<1	5.84	0.01	24.70	830	<2	0.02	2516	21	13	8	<0.01	15	<10	39
44552	1	2.60	<10	7.7	<5	0.97	2	105	1486	<1	7.23	0.02	22.24	1232	<2	0.02	1977	273	14	91	0.15	94	<10	41
44553	<1	0.23	<10	5.9	<5	0.14	1	96	1203	<1	5.33	0.01	23.30	594	<2	0.02	1930	33	11	6	0.01	20	<10	28
44554	<1	0.08	<10	6.0	<5	0.23	2	102	1184	<1	5.38	0.01	23.98	634	<2	0.02	2270	18	11	4	<0.01	16	<10	39
44555	<1	0.20	<10	6.1	<5	0.72	2	102	1307	<1	5.72	0.01	24.31	852	<2	0.02	2281	34	14	7	0.01	17	<10	33
44556	1	0.72	<10	7.0	<5	0.26	2	96	963	35	6.05	0.01	21.98	741	<2	0.02	2004	106	11	6	0.04	38	<10	37
44557	<1	9.41	24	7.6	<5	5.44	1	48	185	20	7.14	0.06	12.35	1493	<2	0.08	133	1076	<2	1096	0.46	285	<10	47
44558	<1	0.65	<10	6.6	<5	2.01	2	98	1090	3	5.73	0.01	21.28	983	<2	0.02	2004	73	10	37	0.03	31	<10	35
44559	1	0.12	39	6.9	<5	2.53	2	114	886	20	6.07	0.01	20.53	974	3	0.03	2232	18	28	39	0.01	21	<10	46
44560	<1	8.19	258	7.7	<5	1.81	1	55	178	76	6.96	0.15	16.66	1156	<2	0.05	340	896	<2	235	0.44	265	<10	49
44561	<1	0.09	<10	5.7	<5	0.18	2	108	1096	<1	5.21	<0.01	23.94	685	<2	0.01	2383	23	12	2	<0.01	14	<10	35
44562	<1	6.88	121	7.7	<5	2.10	1	66	485	41	6.91	0.11	16.36	1194	<2	0.04	682	765	4	641	0.38	230	<10	49
44563	<1	0.16	10	6.3	<5	0.05	2	118	1749	<1	5.77	<0.01	23.71	679	<2	0.01	2402	39	13	3	0.01	16	<10	37
44564	<1	0.08	<10	5.1	<5	0.25	1	90	1092	<1	4.61	<0.01	23.68	657	3	0.01	2234	31	12	3	<0.01	13	<10	28

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2560RR

Date : Nov-25-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
44565	<1	2.20	25	6.1	<5	1.14	1	88	1095	<1	5.54	0.07	21.52	851	<2	0.02	1794	299	8	468	0.13	80	<10	34
44566	1	0.08	18	5.2	<5	0.03	1	99	593	<1	4.66	0.01	23.92	487	<2	0.01	2119	32	9	4	<0.01	13	<10	24
44567	<1	8.03	117	8.0	<5	5.04	1	66	471	<1	7.24	0.43	12.01	1026	<2	0.03	551	944	<2	2307	0.46	299	<10	44
44568	<1	8.21	813	8.7	<5	3.92	1	63	916	<1	7.72	1.36	12.11	2232	<2	0.12	602	1272	<2	1707	0.46	251	<10	133
44569	<1	8.04	1884	8.4	<5	4.45	1	42	391	13	5.12	4.07	5.38	1745	<2	1.51	229	2197	14	895	0.46	157	<10	133
44585	1	0.19	19	6.3	<5	0.56	2	108	1117	5	5.80	0.04	23.56	1097	<2	0.02	2262	56	14	32	0.01	17	<10	51
44586	1	0.10	12	6.4	<5	0.14	2	100	1120	<1	5.98	0.02	23.75	789	<2	0.02	2076	40	13	14	0.01	17	11	36
44587	<1	0.17	19	6.4	<5	0.26	2	113	2257	<1	6.06	0.01	24.06	926	<2	0.02	2244	31	13	34	<0.01	21	<10	48
44588	<1	0.54	104	6.7	<5	1.36	2	103	2177	<1	6.02	0.22	18.52	1691	<2	0.14	1944	162	34	119	0.03	22	<10	110
44589	1	0.12	85	5.4	<5	1.03	1	90	2273	<1	4.91	0.01	18.70	1655	3	0.02	1856	34	15	60	<0.01	13	<10	127
44590	1	0.16	99	4.6	<5	1.44	1	73	906	<1	4.04	0.01	17.37	1772	<2	0.03	1613	22	27	110	<0.01	16	<10	145
44591	1	0.25	22	4.9	<5	0.29	1	71	564	<1	4.14	0.01	17.60	1083	<2	0.03	1672	27	18	20	<0.01	20	<10	157
44592	<1	0.11	39	5.5	<5	0.91	1	91	1026	<1	4.80	0.01	19.42	1208	<2	0.02	1906	34	22	95	<0.01	15	<10	101
44593	<1	0.09	<10	6.5	<5	0.39	2	107	1593	4	5.96	0.01	23.78	1022	<2	0.01	2219	38	14	51	<0.01	17	<10	56
44594	<1	0.08	25	7.0	<5	0.70	2	114	1969	4	6.51	<0.01	23.15	998	<2	0.01	2247	38	12	106	<0.01	15	<10	59
44595	<1	0.08	27	5.6	<5	1.91	1	98	1104	<1	5.08	0.01	20.77	933	<2	0.02	1978	21	13	142	<0.01	15	<10	45
44596	<1	0.15	19	4.8	<5	6.99	1	68	1263	<1	4.14	0.01	14.96	1769	<2	0.03	1534	18	12	144	<0.01	15	<10	93
Duplicates:																								
44503	1	0.23	156	6.2	<5	1.17	2	101	1197	<1	5.39	0.04	20.34	699	<2	0.03	2155	28	43	34	<0.01	22	<10	83
44514	<1	0.13	10	6.6	<5	2.65	2	109	1174	<1	5.65	0.01	21.74	1374	<2	0.02	2312	23	16	35	<0.01	22	<10	60
44524	<1	0.13	<10	6.3	<5	0.33	2	115	1806	<1	6.03	<0.01	24.22	1088	<2	0.01	2343	15	14	10	<0.01	20	<10	52
44529	1	0.12	<10	5.5	<5	0.99	2	109	1064	<1	5.22	0.01	23.67	938	<2	0.01	2228	14	12	45	<0.01	17	<10	40
44538	1	0.07	<10	5.5	<5	0.39	2	111	1282	<1	5.26	0.01	23.21	656	<2	0.01	2207	11	13	20	<0.01	13	<10	37
44548	<1	0.08	<10	5.6	<5	0.04	2	115	1316	<1	5.29	0.01	24.22	754	<2	0.02	2289	<10	12	3	<0.01	15	<10	29
44553	1	0.23	<10	5.9	<5	0.13	2	95	933	<1	5.33	0.01	23.04	591	<2	0.02	1922	36	11	5	0.01	22	<10	30
44562	<1	6.30	125	6.9	<5	1.95	1	61	541	40	6.35	0.10	14.96	1090	<2	0.04	628	658	2	588	0.35	209	<10	44
44587	<1	0.15	18	6.1	<5	0.24	2	103	1916	<1	5.55	0.01	22.48	849	<2	0.02	2037	29	13	31	<0.01	19	<10	41
44592	<1	0.11	26	5.6	<5	0.94	1	94	715	<1	4.93	0.01	20.02	1247	<2	0.02	1977	23	20	98	<0.01	17	<10	105
Standards:																								
BLANK	<1	<0.01	<10	<0.5	<5	<0.01	<1	1	<1	<1	0.01	<0.01	<0.01	<5	<2	0.01	1	<10	<2	<1	<0.01	<1	<10	<2

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2560RR

Date : Nov-25-08

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
CH-4	2	7.79	498	6.9	<5	2.04	2	35	99	2057	5.84	1.84	1.64	487	<2	3.29	88	574	15	212	0.30	106	<10	220

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2654RR

Date : Nov-26-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
44604	1	0.11	31	3.0	<5	2.17	2	99	1182	3	5.03	0.01	21.14	959	<2	0.02	2258	21	25	31	<0.01	18	<10	55
44605	1	0.12	<10	2.5	<5	2.16	2	88	1097	4	4.83	0.01	22.16	864	4	0.01	1948	16	19	90	<0.01	19	10	48
44606	1	0.09	42	2.6	<5	1.58	2	87	1261	1	4.96	0.01	22.37	865	4	0.01	2032	11	16	60	<0.01	16	<10	41
44607	1	0.14	20	2.9	<5	0.64	2	99	2220	<1	5.58	<0.01	22.60	962	<2	0.01	2377	21	24	15	<0.01	15	10	52
44608	2	0.15	48	2.7	<5	0.50	2	96	1380	<1	5.27	0.01	23.30	826	5	0.01	2236	13	22	21	<0.01	19	<10	62
44609	1	0.16	<10	2.4	<5	0.46	2	91	1207	<1	4.85	0.01	23.27	696	2	0.01	2111	<10	17	29	<0.01	19	<10	38
44610	<1	0.10	10	2.6	<5	0.48	2	105	1404	<1	5.02	0.01	23.46	803	2	0.01	2470	17	7	20	<0.01	15	<10	46
44611	<1	0.08	<10	2.5	<5	0.67	2	96	1097	<1	4.74	<0.01	23.02	807	2	0.01	2142	12	7	19	<0.01	14	11	40
44612	1	0.15	85	2.6	<5	0.93	2	92	993	1	4.80	0.01	21.66	1152	4	0.01	2070	14	39	38	<0.01	19	14	96
44613	<1	0.14	77	2.4	<5	1.70	2	87	1082	<1	4.53	0.01	21.88	1304	3	0.02	1970	16	22	400	<0.01	17	<10	73
44614	1	0.16	15	2.8	<5	1.11	2	93	995	2	5.18	0.01	21.98	1048	2	0.01	2171	25	13	63	<0.01	20	<10	60
44615	1	0.13	10	2.7	<5	1.23	2	99	1064	1	5.31	0.01	24.13	872	<2	0.01	2217	29	5	83	<0.01	21	<10	47
44616	1	0.12	12	2.4	<5	1.32	1	97	1052	<1	4.76	<0.01	22.91	862	4	0.01	2298	13	5	110	<0.01	20	11	50
44617	1	0.10	20	2.5	<5	0.75	2	99	981	<1	4.90	<0.01	23.38	907	6	0.01	2389	22	10	85	<0.01	18	<10	44
44618	<1	0.17	95	2.7	<5	0.83	2	98	1694	<1	5.33	0.01	22.35	982	5	0.01	2230	19	50	83	<0.01	18	<10	87
44619	1	0.11	53	2.6	<5	0.83	2	94	1429	<1	5.16	<0.01	22.72	951	2	0.01	2190	13	35	200	<0.01	20	<10	71
44620	1	0.14	135	2.9	<5	1.05	2	101	1644	<1	5.84	0.01	23.72	1031	3	0.01	2060	25	49	373	<0.01	19	<10	70
44621	1	0.14	48	2.3	<5	0.42	2	100	1234	<1	4.53	<0.01	22.69	793	2	0.01	2076	21	17	235	<0.01	20	<10	50
44622	1	0.14	50	2.2	<5	0.71	2	91	988	<1	4.39	<0.01	22.88	897	4	0.01	1907	23	14	309	<0.01	19	10	52
44623	1	0.09	14	2.3	<5	0.21	2	100	942	<1	4.52	<0.01	24.11	872	<2	0.01	2261	22	12	141	<0.01	16	<10	33
44624	<1	0.09	30	2.5	<5	0.42	2	103	1434	<1	4.89	<0.01	23.90	971	5	0.01	2271	19	9	612	<0.01	15	<10	38
44625	1	0.11	11	2.6	<5	0.49	2	98	1202	<1	5.03	<0.01	23.44	1059	3	0.01	2144	13	20	211	<0.01	16	<10	41
44626	1	0.14	52	2.8	<5	0.91	2	102	1108	<1	5.37	0.01	24.65	1136	3	0.01	2275	17	15	162	<0.01	21	11	54
44627	<1	1.47	62	2.8	<5	2.07	2	93	968	57	5.19	0.02	19.47	1555	6	0.01	1756	198	33	372	0.05	53	<10	98
44628	<1	0.11	21	2.8	<5	0.68	2	102	1155	4	5.35	0.01	22.64	1160	<2	0.01	2193	<10	19	63	<0.01	18	<10	64
44629	<1	5.32	13	3.5	<5	0.73	2	75	843	4	6.64	0.03	16.66	1308	5	0.04	1318	611	<2	52	0.25	154	13	56
44630	<1	3.79	236	3.3	<5	3.01	2	72	702	22	6.27	0.52	15.46	2163	16	0.20	1206	406	20	235	0.18	113	<10	102
44631	<1	0.15	<10	2.5	<5	2.90	2	89	1096	1	4.56	0.01	19.00	791	<2	0.01	1824	20	14	254	<0.01	18	<10	36
44632	<1	0.12	15	2.5	<5	4.34	2	93	1236	<1	4.92	0.01	19.79	745	<2	0.01	1966	10	13	123	<0.01	16	<10	38
44633	<1	0.28	<10	2.7	<5	2.43	2	101	1400	1	5.08	0.01	20.79	843	<2	0.01	2066	19	13	44	0.01	19	<10	37

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2654RR

Date : Nov-26-08

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
44634	1	0.09	20	3.0	<5	1.10	2	103	1159	<1	4.93	0.01	21.66	879	<2	0.01	2190	14	15	21	<0.01	21	<10	35
44635	<1	0.16	<10	3.0	<5	0.44	2	109	1424	3	5.53	0.01	19.71	659	<2	0.02	2226	17	23	19	<0.01	21	17	40
44636	<1	8.89	32	3.4	<5	0.36	1	46	178	<1	6.72	0.18	17.37	1544	<2	0.24	235	1066	<2	18	0.39	230	13	48
44637	<1	0.28	29	2.9	<5	0.35	2	100	1299	22	5.36	0.01	21.74	538	<2	0.01	2144	20	18	45	0.01	24	25	24
44638	<1	0.73	10	2.6	<5	1.47	2	100	1427	6	5.11	0.02	21.09	896	<2	0.01	1917	99	4	188	0.03	29	17	29
44639	<1	0.10	<10	2.3	<5	1.64	1	92	1205	2	4.45	0.01	21.52	815	<2	0.01	1942	11	8	186	<0.01	16	13	33
44640	<1	0.11	44	2.5	<5	0.51	2	88	1294	<1	4.92	0.01	21.82	850	<2	0.01	2079	18	12	66	<0.01	18	19	45
44641	<1	0.14	<10	2.4	<5	0.59	2	85	1204	<1	4.81	0.01	22.59	768	<2	0.01	2066	<10	11	95	<0.01	19	16	29
44642	<1	0.29	27	2.2	<5	0.59	2	90	944	<1	4.44	0.02	22.55	601	<2	0.01	2048	22	10	55	0.01	19	17	37
44643	1	0.10	11	2.5	<5	0.70	2	101	1433	<1	4.95	0.01	23.97	863	<2	0.01	2278	17	13	90	<0.01	17	18	38
44644	<1	0.11	40	2.9	<5	0.60	2	101	1286	<1	5.82	0.01	22.63	844	<2	0.01	2031	13	24	22	<0.01	20	26	44
44645	<1	0.18	<10	2.7	<5	1.32	2	101	1174	<1	5.23	0.01	21.58	884	<2	0.01	2061	14	22	28	0.01	23	12	40
44646	1	0.40	25	2.7	<5	2.93	2	95	835	<1	4.98	0.01	19.76	895	<2	0.01	1984	44	38	154	0.02	24	<10	41
44647	<1	0.21	28	3.0	<5	1.35	2	103	1319	4	5.37	0.01	21.08	937	<2	0.02	2076	20	30	34	0.01	24	13	41
44648	1	0.16	<10	2.5	<5	0.92	2	109	1200	6	5.29	0.01	22.73	718	<2	0.01	2177	14	19	59	<0.01	24	15	35
44649	<1	0.12	<10	2.9	<5	0.91	2	108	1958	5	5.93	0.01	21.62	931	<2	0.01	2060	13	19	68	<0.01	19	12	47
44650	<1	0.10	<10	2.9	<5	0.49	2	110	1622	6	5.90	0.01	22.44	814	<2	0.01	2233	12	19	31	<0.01	19	16	41
44651	<1	0.09	<10	2.5	<5	0.72	2	108	1431	5	5.24	0.01	22.72	985	<2	0.01	2160	<10	15	32	<0.01	17	15	37
44652	<1	0.10	35	2.7	<5	1.03	2	110	998	8	5.40	0.01	22.84	1002	<2	0.01	2215	21	12	46	<0.01	19	<10	46
44653	<1	0.10	<10	2.9	<5	1.34	2	104	1339	1	5.45	0.01	22.03	997	<2	0.01	2061	12	3	65	<0.01	19	<10	41
44654	<1	0.11	46	3.2	<5	1.03	2	104	1078	2	5.43	0.01	21.58	990	<2	0.01	2116	14	20	62	<0.01	20	11	51
44655	<1	0.39	30	3.0	<5	2.19	2	83	1371	50	4.44	0.02	17.63	764	5	0.03	1787	21	3	89	0.01	20	<10	57
44656	<1	6.86	3429	2.5	<5	1.04	1	33	227	11	2.81	4.29	6.57	550	5	0.77	391	312	<2	1798	0.14	73	<10	42
44657	<1	7.69	884	2.5	<5	0.34	1	14	63	84	1.89	5.91	1.90	215	<2	0.81	61	338	<2	248	0.12	61	<10	27
44658	<1	4.46	543	4.1	<5	6.43	2	29	414	33	4.67	1.94	6.85	1002	<2	0.83	602	272	<2	415	0.11	76	<10	54
44659	<1	8.97	809	3.6	<5	3.80	1	26	56	67	5.04	3.41	2.45	649	<2	2.80	28	931	<2	681	0.37	197	<10	40
44660	<1	2.27	138	4.0	<5	8.19	2	45	613	23	5.39	0.82	7.73	1154	<2	0.42	996	88	55	233	0.04	56	<10	74
44661	<1	3.54	349	2.0	<5	2.70	1	29	276	19	2.33	1.70	5.69	984	4	0.78	464	53	76	226	0.06	48	<10	107
44662	<1	6.55	213	3.7	<5	4.88	2	47	396	23	5.63	1.34	7.09	1236	<2	1.46	415	616	9	399	0.29	186	<10	89
44663	<1	8.61	361	4.2	<5	4.60	5	38	73	78	5.73	2.37	4.32	1974	12	1.80	64	757	139	499	0.37	257	<10	625

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2654RR

Date : Nov-26-08

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
44664	1	7.24	408	3.6	<5	3.97	6	34	173	45	5.37	2.22	5.07	2842	5	0.88	181	606	129	376	0.29	181	<10	1113
44665	<1	0.85	40	3.8	<5	0.86	2	95	1191	4	5.43	0.38	20.56	1023	2	0.30	1943	60	7	58	0.01	26	<10	51
44666	<1	0.25	<10	2.7	<5	0.70	2	103	1506	1	5.16	0.02	22.19	882	<2	0.02	2033	21	5	71	<0.01	25	10	48
44667	<1	0.18	10	2.6	<5	0.86	2	104	1433	4	4.90	0.02	22.00	1239	<2	0.02	2029	25	3	191	<0.01	22	<10	67
44668	<1	0.21	68	2.6	<5	0.64	2	103	1259	3	5.28	0.02	22.62	900	<2	0.02	2164	35	26	96	<0.01	25	<10	69
44669	<1	0.21	39	2.5	<5	1.46	2	98	1516	3	4.96	0.02	21.87	909	<2	0.02	2070	33	27	214	<0.01	22	<10	55
44670	<1	0.32	18	2.9	<5	1.12	2	107	1517	2	5.58	0.02	21.58	1026	<2	0.02	2266	39	11	118	0.01	32	<10	52
44671	<1	0.11	10	2.6	<5	0.60	2	116	1294	2	5.18	0.02	23.28	973	<2	0.01	2287	23	13	85	<0.01	19	<10	41
44672	<1	0.12	45	2.8	<5	0.87	2	112	1185	2	5.31	0.02	23.04	955	<2	0.01	2138	18	27	102	<0.01	18	<10	48
44673	<1	0.10	11	2.6	<5	0.66	2	109	1268	6	5.15	0.01	22.03	1044	<2	0.01	2148	32	22	59	<0.01	17	<10	54
44674	<1	0.09	40	3.0	<5	0.63	2	116	1384	1	5.94	0.01	22.62	990	<2	0.02	2317	29	27	30	<0.01	16	<10	46
44675	<1	0.15	64	2.9	<5	0.86	2	106	1173	1	5.40	0.02	21.44	889	<2	0.02	2171	31	22	44	<0.01	19	<10	49
44676	<1	7.05	26	3.5	<5	0.33	2	47	190	<1	6.32	0.02	18.77	698	<2	0.01	274	602	13	71	0.34	226	<10	45
44677	<1	6.49	31	3.7	<5	0.38	2	52	162	<1	6.79	0.02	18.77	952	<2	0.01	336	598	<2	58	0.33	220	12	54
44678	<1	2.31	46	3.0	<5	2.15	2	106	1078	10	5.75	0.02	19.71	1193	85	0.02	1844	252	15	134	0.10	90	<10	67
44679	<1	2.02	22	2.8	<5	2.27	2	98	825	2	5.42	0.01	18.74	1281	<2	0.02	1687	192	19	201	0.09	78	<10	59
44680	<1	6.19	10	3.6	<5	0.36	2	70	272	<1	6.66	0.02	19.61	1186	<2	0.02	724	567	<2	58	0.30	202	<10	53
44681	<1	0.11	<10	2.9	<5	0.39	2	111	948	<1	5.64	0.01	22.98	1033	<2	0.01	2244	17	17	27	<0.01	19	11	40
44682	<1	0.23	<10	2.9	<5	0.29	2	114	933	<1	5.72	0.01	24.33	901	<2	0.02	2306	17	11	16	0.01	24	<10	37
44683	<1	0.10	11	2.5	<5	1.31	2	94	783	7	4.95	0.01	22.49	878	<2	0.02	2003	10	20	196	<0.01	19	<10	35
44684	1	0.10	<10	2.8	<5	0.47	2	101	715	2	5.50	0.01	22.96	815	<2	0.01	2127	<10	26	56	<0.01	20	<10	32
44685	<1	0.11	<10	2.8	<5	0.34	2	104	911	<1	5.42	0.01	23.61	794	<2	0.01	2175	13	16	68	<0.01	21	<10	34
44686	<1	0.07	<10	2.8	<5	0.12	2	103	985	<1	5.55	0.01	24.10	952	2	0.01	2304	13	18	24	<0.01	16	<10	37
44687	<1	0.10	<10	2.6	<5	0.33	2	107	849	<1	5.02	<0.01	23.41	901	<2	0.01	2189	14	12	40	<0.01	17	<10	33
44688	1	0.11	<10	3.0	<5	0.34	2	108	1075	<1	5.70	0.01	23.29	937	<2	0.01	2157	19	7	40	<0.01	19	<10	46
44689	<1	0.09	<10	2.5	<5	0.76	2	96	1031	<1	4.83	0.01	21.41	1610	<2	0.01	1974	12	17	64	<0.01	16	10	49
44690	<1	0.06	<10	2.8	<5	0.19	2	119	1063	<1	5.95	0.01	24.60	933	<2	0.01	2213	<10	10	38	<0.01	16	<10	34
44691	<1	0.07	<10	2.5	<5	0.29	2	100	678	<1	4.88	0.01	21.91	1005	<2	0.01	2061	<10	19	31	<0.01	15	<10	40
44692	<1	0.07	<10	2.6	<5	0.53	2	101	1065	<1	4.89	0.01	21.52	1565	<2	0.01	2077	<10	13	46	<0.01	13	<10	50
44693	<1	0.06	<10	2.7	<5	0.31	2	108	1205	<1	5.27	0.01	22.84	1165	<2	0.01	2289	12	12	31	<0.01	15	15	44

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2654RR

Date : Nov-26-08

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
44694	<1	0.07	<10	2.4	<5	0.74	2	89	676	2	4.42	0.01	19.49	1020	<2	0.01	1903	<10	12	63	<0.01	15	<10	62
44695	<1	0.07	<10	2.2	<5	1.44	2	96	604	1	4.15	<0.01	20.48	1219	<2	0.01	1890	18	9	134	<0.01	13	<10	43
44696	<1	0.08	<10	2.1	<5	0.94	2	103	582	3	3.87	0.01	20.97	1244	<2	0.01	2057	<10	18	58	<0.01	12	<10	52
44697	<1	0.10	<10	1.6	<5	1.46	1	87	807	7	3.04	0.01	19.51	1688	3	0.02	1771	<10	8	91	<0.01	11	<10	93
44698	<1	0.09	<10	2.6	<5	0.61	2	116	599	<1	5.15	0.01	23.78	805	<2	0.01	2461	<10	23	16	<0.01	16	<10	40
44699	<1	0.09	<10	2.6	<5	0.64	2	102	728	<1	5.13	<0.01	22.91	734	<2	0.01	2230	<10	12	22	<0.01	15	<10	36
44700	<1	0.07	<10	2.8	<5	2.54	2	90	811	<1	5.29	0.01	21.37	641	<2	0.02	2240	<10	5	32	<0.01	17	<10	37
Duplicates:																								
44604	1	0.11	37	2.9	<5	2.15	2	99	1121	3	5.04	0.01	21.19	962	6	0.01	2268	20	18	32	<0.01	17	10	60
44613	1	0.14	80	2.5	<5	1.76	2	88	1145	<1	4.72	0.01	22.67	1347	<2	0.01	2019	27	27	412	<0.01	16	<10	77
44623	<1	0.10	14	2.4	<5	0.21	2	101	861	<1	4.53	<0.01	24.11	867	<2	0.01	2209	26	8	140	<0.01	17	<10	39
44628	<1	0.11	16	2.7	<5	0.67	2	102	902	2	5.37	0.01	22.63	1164	<2	0.01	2207	21	20	62	<0.01	20	<10	65
44637	<1	0.28	25	3.0	<5	0.36	2	104	866	23	5.59	0.01	22.38	559	<2	0.01	2230	29	16	47	0.01	26	15	29
44647	<1	0.21	28	2.9	<5	1.34	2	104	1147	4	5.35	0.01	20.99	934	<2	0.02	2080	14	16	34	0.01	26	<10	38
44652	<1	0.10	35	2.7	<5	1.01	2	108	1276	7	5.38	0.01	22.68	997	2	0.01	2198	25	13	47	<0.01	18	<10	46
44661	<1	3.57	354	1.9	<5	2.71	1	29	634	18	2.34	1.72	5.77	991	<2	0.79	463	54	64	229	0.05	46	<10	110
44671	<1	0.10	<10	2.6	<5	0.58	2	111	1207	1	4.99	0.01	22.45	939	<2	0.01	2217	23	4	79	<0.01	17	<10	39
44676	<1	7.10	27	3.6	<5	0.32	2	48	181	<1	6.38	0.02	18.92	693	<2	0.01	277	617	6	69	0.34	227	<10	46
44685	<1	0.11	<10	2.6	<5	0.32	2	101	978	<1	5.25	<0.01	22.93	773	<2	0.01	2088	15	22	66	<0.01	19	<10	34
44695	<1	0.08	<10	2.2	<5	1.46	2	98	524	<1	4.23	0.01	20.90	1242	<2	0.02	1941	12	11	137	<0.01	14	10	44
44700	<1	0.07	<10	2.8	<5	2.52	2	91	722	<1	5.23	0.01	21.23	636	<2	0.02	2196	<10	6	32	<0.01	17	<10	37
Standards:																								
Blank	<1	0.01	<10	<0.5	<5	<0.01	<1	1	1	1	<0.01	<0.01	<0.01	<5	2	0.01	1	<10	<2	<1	<0.01	<1	<10	<2
CH-4	2	7.57	477	3.5	<5	1.94	3	32	74	1985	5.44	1.79	1.46	463	<2	3.15	61	609	14	204	0.28	103	<10	224

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2665RR

Date : Nov-26-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
44701	<1	0.11	<10	6.1	<5	5.52	2	92	904	<1	5.21	0.04	19.99	882	<2	0.03	1818	21	17	89	<0.01	15	<10	43
44702	2	0.08	<10	6.6	<5	4.73	1	105	923	<1	5.62	0.03	20.16	950	<2	0.03	1956	17	6	68	<0.01	15	<10	45
44703	<1	0.06	<10	6.6	<5	3.18	2	100	1361	<1	5.65	0.03	19.45	699	<2	0.03	2139	27	5	80	<0.01	14	<10	37
44704	<1	0.10	<10	8.3	<5	6.67	2	108	1395	<1	7.08	0.02	16.85	925	<2	0.03	2023	18	7	104	0.01	22	<10	56
44715	<1	0.27	10	7.9	<5	2.96	2	116	1251	<1	6.74	0.04	20.84	1239	<2	0.03	2099	77	12	34	0.01	21	<10	26
44716	<1	0.10	<10	7.2	<5	5.69	2	107	1454	<1	6.09	0.03	19.41	1114	4	0.03	1889	35	26	119	<0.01	19	<10	45
44717	1	0.12	12	7.0	<5	2.28	2	111	1337	<1	6.12	0.03	21.34	871	56	0.02	1855	36	14	85	<0.01	19	14	30
44718	<1	0.17	11	7.1	<5	1.23	2	124	1796	11	6.35	0.04	23.76	908	151	0.03	2143	34	10	25	<0.01	19	<10	29
44719	<1	0.16	27	7.1	<5	0.88	2	110	1795	<1	6.52	0.03	23.16	825	19	0.03	2140	40	11	28	<0.01	19	<10	24
44720	<1	0.21	<10	8.0	<5	0.60	2	126	2582	<1	6.99	0.03	24.59	1058	25	0.02	2043	38	2	103	<0.01	21	<10	34
44721	1	0.13	11	6.3	<5	1.30	1	105	1747	<1	5.61	0.02	22.25	1079	<2	0.03	2032	33	4	239	<0.01	19	<10	35
44722	<1	0.12	<10	6.3	<5	0.72	2	103	1444	<1	5.54	0.03	24.00	1188	<2	0.02	2089	39	19	28	<0.01	18	12	68
44723	<1	1.18	<10	5.8	<5	1.42	1	101	1269	<1	5.26	0.03	23.51	1242	<2	0.02	1876	141	45	111	0.06	52	11	52
44724	<1	0.19	10	6.3	<5	1.37	2	99	1977	<1	5.86	0.02	23.18	1079	<2	0.02	1863	50	12	73	0.01	20	11	31
44725	<1	0.14	<10	6.0	<5	0.32	1	111	1830	<1	5.53	0.03	24.32	873	<2	0.02	2084	33	2	40	<0.01	17	<10	33
44726	1	0.12	<10	5.9	<5	0.43	1	109	1807	<1	5.42	0.03	24.42	848	<2	0.02	2157	45	8	49	<0.01	15	10	33
44727	1	0.16	<10	6.3	<5	0.60	1	128	2847	<1	5.85	0.04	25.71	1250	<2	0.02	2410	45	8	47	<0.01	15	16	44
44728	<1	0.14	<10	5.9	<5	0.80	1	110	2218	<1	5.16	0.02	23.38	1197	<2	0.02	2042	29	<2	69	<0.01	18	<10	38
44729	<1	0.17	<10	6.0	<5	1.31	1	115	2105	<1	5.43	0.02	23.16	1080	<2	0.02	2102	<10	6	121	<0.01	19	<10	39
44730	<1	0.15	<10	5.7	<5	1.13	1	105	1733	<1	5.32	0.02	22.88	865	<2	0.02	1969	44	10	81	<0.01	20	<10	31
44731	<1	0.11	<10	6.0	<5	0.70	1	114	1967	<1	5.67	0.02	23.82	1359	<2	0.02	2190	48	4	87	<0.01	17	<10	42
44732	<1	0.14	<10	6.3	<5	0.71	2	120	4435	<1	6.14	0.03	23.52	1011	<2	0.02	2154	39	10	63	<0.01	18	<10	64
44733	<1	2.74	692	7.0	<5	2.07	2	85	1999	<1	5.88	1.24	19.04	1169	<2	0.44	1497	831	5	445	0.19	74	<10	59
44734	<1	0.72	<10	6.2	<5	1.33	1	106	2534	<1	5.81	0.03	24.31	1142	<2	0.03	1967	70	4	44	0.02	25	19	53
44735	<1	1.18	15	5.4	<5	1.65	2	95	1962	<1	5.51	0.02	22.66	1010	<2	0.02	1896	102	19	81	0.04	34	<10	49
44736	<1	0.16	<10	5.1	<5	2.40	2	100	1731	<1	5.13	0.01	22.22	1039	<2	0.02	2128	19	14	94	<0.01	15	<10	39
44737	<1	0.10	<10	5.2	<5	1.50	2	104	1724	<1	5.43	0.01	24.13	1010	<2	0.02	2116	28	16	49	<0.01	14	15	40
44738	<1	0.11	<10	4.9	<5	1.42	2	100	1446	<1	4.97	<0.01	23.59	1043	<2	0.02	2153	13	8	69	<0.01	17	<10	37
44739	<1	0.08	<10	5.5	<5	0.93	2	98	1648	<1	5.48	<0.01	23.87	1086	<2	0.02	2115	13	13	28	<0.01	15	<10	37
44740	<1	0.05	<10	4.9	<5	1.07	1	86	861	<1	4.72	<0.01	21.40	920	<2	0.02	2101	<10	4	33	<0.01	12	<10	29

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2665RR

Date : Nov-26-08

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
44741	<1	0.10	<10	5.1	<5	1.26	1	85	1607	<1	4.91	<0.01	22.33	1022	<2	0.02	2093	19	8	40	<0.01	13	<10	44
44742	<1	0.11	<10	5.1	<5	2.91	2	84	1626	22	4.89	<0.01	21.57	1110	<2	0.01	1963	18	17	167	<0.01	13	<10	48
44743	<1	2.65	282	5.3	<5	4.90	1	75	1099	93	4.51	0.78	13.99	932	3	0.06	1023	1022	9	151	0.19	71	<10	49
44744	<1	1.74	198	4.7	<5	1.98	1	62	1194	22	4.12	1.22	14.58	580	5	0.07	1316	28	12	111	0.02	19	<10	27
44745	<1	3.65	222	4.8	<5	0.91	1	54	1231	14	3.81	1.08	12.70	558	47	0.40	1008	11	<2	216	0.03	34	<10	35
44746	<1	0.19	<10	5.6	<5	0.19	2	110	1759	<1	5.87	0.01	25.21	949	<2	0.02	2258	24	13	13	<0.01	18	<10	30
44747	1	0.15	<10	5.6	<5	0.45	2	106	1834	14	5.74	0.01	24.02	691	<2	0.03	2074	17	14	21	<0.01	19	<10	21
44748	<1	0.15	<10	5.9	<5	0.35	2	112	1970	<1	6.34	0.01	25.54	1076	<2	0.02	2213	18	17	24	<0.01	19	11	29
44749	<1	0.12	<10	5.5	<5	0.30	2	112	1710	<1	5.84	0.01	26.01	1001	<2	0.02	2336	29	8	22	<0.01	16	<10	24
44750	<1	0.13	<10	5.3	<5	0.34	2	106	1643	<1	5.46	0.01	24.92	824	2	0.02	2103	28	12	21	<0.01	17	<10	25
44751	<1	0.12	<10	5.9	<5	0.26	2	109	1812	<1	5.70	0.05	25.54	936	<2	0.01	2215	13	15	16	<0.01	16	<10	21
44752	<1	0.12	<10	5.9	<5	0.21	2	114	1962	<1	6.10	0.01	26.28	933	<2	0.01	2368	13	16	16	<0.01	17	<10	23
44753	<1	0.12	<10	5.7	<5	0.28	2	112	1999	<1	5.90	0.01	25.99	1075	<2	0.01	2381	18	17	28	<0.01	14	<10	24
44754	<1	0.15	<10	5.4	<5	0.26	2	109	1862	<1	5.67	0.01	24.98	721	<2	0.02	2236	27	14	14	<0.01	20	<10	23
44755	<1	0.15	<10	5.0	<5	0.30	2	105	1642	<1	5.27	0.01	24.28	750	<2	0.02	2142	10	16	14	<0.01	20	<10	25
44756	<1	0.14	<10	5.2	<5	0.34	1	108	1553	<1	5.42	<0.01	24.18	758	<2	0.02	2199	13	13	13	<0.01	20	<10	23
44757	<1	0.12	<10	5.1	<5	0.24	2	107	1377	<1	5.20	<0.01	23.89	820	<2	0.01	2169	23	13	11	<0.01	18	<10	25
44758	<1	0.10	<10	5.4	<5	0.62	2	105	1514	<1	5.65	<0.01	24.26	831	<2	0.01	2109	26	16	37	<0.01	16	<10	25
44759	<1	0.12	<10	6.0	<5	0.44	1	111	1601	4	5.69	0.01	25.50	813	<2	0.02	2195	24	16	24	<0.01	17	<10	26
44760	<1	0.14	<10	5.8	<5	0.50	1	111	1648	5	5.59	0.01	25.24	766	<2	0.02	2289	15	14	21	<0.01	19	<10	25
44761	<1	0.13	<10	5.9	<5	0.28	1	115	1732	5	5.73	0.01	25.65	849	<2	0.02	2323	22	16	15	<0.01	17	10	25
44762	<1	0.12	<10	6.2	<5	0.31	1	115	1594	5	5.94	0.01	25.71	858	<2	0.02	2401	13	18	16	<0.01	18	10	25
44763	<1	0.10	<10	6.3	<5	0.36	2	116	1389	3	6.04	0.01	25.60	779	<2	0.02	2281	17	19	22	<0.01	17	<10	19
44764	<1	0.08	<10	5.6	<5	0.76	1	114	1276	2	5.32	0.01	25.18	839	<2	0.02	2311	20	18	51	<0.01	15	<10	23
44765	<1	1.34	10	6.4	<5	0.59	1	108	2236	1	6.11	0.01	24.52	1058	<2	0.02	2211	138	14	63	0.06	61	12	25
44766	<1	0.60	<10	5.8	<5	3.36	1	103	1590	<1	5.52	0.01	21.30	784	<2	0.03	1963	67	14	152	0.03	34	10	26
44767	<1	2.55	<10	6.1	<5	1.69	1	83	1223	<1	5.70	0.01	19.48	731	<2	0.02	1427	272	11	161	0.13	91	11	43
44768	<1	0.38	<10	5.7	<5	1.02	1	97	1463	<1	5.30	<0.01	22.08	922	<2	0.01	1932	49	18	114	0.02	23	<10	26
44769	<1	0.12	15	4.9	<5	0.79	1	94	735	5	4.78	0.01	21.66	941	<2	0.01	1947	31	17	81	0.01	13	<10	34
44770	<1	0.06	<10	5.5	<5	0.71	1	100	856	<1	5.33	0.01	22.42	754	<2	0.01	2020	15	27	40	<0.01	13	10	29

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2665RR

Date : Nov-26-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
44771	1	0.05	<10	4.8	<5	1.21	20	85	639	45	4.54	<0.01	19.37	872	3	0.02	1708	19	839	79	<0.01	12	<10	363
44772	<1	0.04	<10	6.1	<5	0.87	2	107	1269	1	5.86	<0.01	23.67	733	<2	0.01	2211	15	18	51	<0.01	10	10	27
44773	<1	0.05	<10	5.9	<5	0.66	2	106	987	<1	5.55	<0.01	24.32	760	<2	0.01	2139	16	16	35	<0.01	11	11	20
44774	<1	0.08	<10	5.4	<5	0.64	1	101	1232	<1	5.23	<0.01	23.61	678	<2	0.01	2128	<10	18	31	<0.01	12	<10	21
44775	<1	0.06	<10	5.9	<5	0.63	1	107	1411	<1	5.57	<0.01	23.55	791	<2	0.01	2150	15	19	28	<0.01	11	<10	24
44776	<1	0.12	<10	5.5	<5	2.17	1	99	1338	<1	5.03	<0.01	21.57	829	<2	0.02	2042	18	18	106	<0.01	12	<10	22
44777	<1	6.07	417	7.1	<5	4.64	1	62	649	6	6.27	1.40	9.19	2337	<2	1.17	781	618	254	379	0.28	175	10	196
44778	<1	3.11	116	5.6	<5	4.26	2	68	1042	1	5.07	0.42	12.79	1770	<2	0.37	1142	340	342	203	0.17	112	19	218
44779	<1	1.72	176	5.8	<5	4.15	1	87	1348	1	5.28	0.45	17.08	1773	<2	0.30	1627	195	49	231	0.08	60	<10	111
44780	1	0.61	<10	5.3	<5	3.26	9	93	1553	51	4.97	0.01	18.45	920	<2	0.03	1886	51	727	132	0.03	33	<10	417
44781	<1	8.50	<10	9.0	<5	0.26	1	69	385	<1	8.16	0.08	16.35	2732	<2	0.19	480	904	12	85	0.54	284	20	108
44782	<1	5.74	<10	7.7	<5	0.21	1	91	524	<1	7.23	0.03	17.01	2926	<2	0.09	1227	614	44	62	0.37	202	14	143
44783	<1	3.62	53	7.1	<5	1.34	1	79	1087	<1	6.29	0.15	17.07	1549	<2	0.09	1166	394	41	110	0.22	131	<10	75
44784	1	0.11	<10	6.0	<5	1.10	2	105	847	<1	5.50	0.02	22.43	827	<2	0.02	1972	50	15	23	<0.01	17	<10	31
44785	<1	0.09	<10	6.2	<5	0.35	1	105	887	<1	5.63	0.02	23.40	872	<2	0.02	1955	32	28	8	<0.01	15	16	29
44786	<1	0.05	<10	6.1	<5	0.21	1	108	658	<1	5.53	0.02	23.58	834	<2	0.01	1991	27	30	4	<0.01	12	<10	24
44787	<1	0.09	<10	5.8	<5	0.35	1	105	1102	<1	5.24	0.02	23.06	793	<2	0.01	1980	44	21	6	<0.01	14	13	27
44788	<1	0.16	<10	6.1	<5	0.45	1	100	1276	<1	5.39	0.02	22.23	729	<2	0.01	1808	37	20	6	<0.01	17	13	25
44789	<1	0.09	<10	6.3	<5	0.63	1	112	1007	<1	5.74	0.02	22.85	823	<2	0.01	2010	36	21	6	<0.01	15	<10	27
44790	1	0.08	<10	6.1	<5	2.40	1	108	1110	<1	5.50	0.02	21.32	1005	<2	0.02	1975	33	29	33	<0.01	16	<10	32
44791	1	9.09	374	8.4	<5	0.36	1	45	146	<1	6.88	1.78	9.78	808	<2	0.86	156	947	<2	284	0.32	268	11	71
44792	<1	8.26	619	7.8	<5	0.62	1	41	211	<1	6.35	1.69	7.10	780	<2	1.28	71	790	<2	419	0.36	240	17	71
44793	1	2.66	85	6.6	<5	5.34	2	93	1307	<1	5.85	0.36	13.65	1408	<2	0.10	1256	248	8	97	0.13	98	10	70
Duplicates:																								
44701	<1	0.10	<10	6.0	<5	5.52	1	91	937	<1	5.24	0.03	20.01	885	<2	0.02	1855	26	20	89	<0.01	15	<10	43
44720	<1	0.20	<10	8.2	<5	0.63	2	129	2744	<1	7.32	0.03	25.61	1103	25	0.02	2128	39	20	107	<0.01	20	15	34
44730	<1	0.15	<10	5.9	<5	1.15	1	108	1763	<1	5.37	0.02	23.15	878	<2	0.01	1990	15	2	75	<0.01	21	14	32
44735	<1	1.12	14	5.2	<5	1.57	1	91	1895	<1	5.22	0.02	21.54	957	<2	0.02	1817	101	16	73	0.04	33	<10	44
44744	<1	1.58	183	4.3	<5	1.84	1	62	1083	10	3.79	1.12	13.56	527	4	0.06	1232	32	9	102	0.01	17	<10	21
44754	<1	0.15	<10	5.4	<5	0.26	2	108	1513	<1	5.57	0.01	24.72	710	<2	0.02	2236	17	15	14	<0.01	20	<10	25

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2665RR

Date : Nov-26-08

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
44759	<1	0.13	12	6.1	<5	0.44	2	113	1610	<1	5.85	0.01	26.21	835	<2	0.02	2285	18	17	24	<0.01	18	10	29
44768	<1	0.39	<10	5.8	<5	1.06	1	102	1505	<1	5.49	0.01	22.86	954	<2	0.02	2030	48	15	119	0.02	24	<10	30
44778	<1	3.19	121	5.9	<5	4.38	2	71	1155	<1	5.22	0.44	13.14	1819	<2	0.39	1187	357	324	209	0.17	115	17	227
44783	<1	3.56	52	7.4	<5	1.32	1	80	1059	<1	6.19	0.15	16.82	1536	<2	0.08	1163	384	39	109	0.21	130	<10	68
44792	<1	8.41	633	7.9	<5	0.63	1	42	186	<1	6.49	1.73	7.28	798	<2	1.33	72	816	<2	428	0.33	247	<10	73
Standards:																								
BLANK	<1	0.01	<10	<0.5	<5	<0.01	<1	1	3	<1	0.01	<0.01	0.01	<5	<2	0.01	1	<10	<2	<1	<0.01	<1	<10	<2
CH-4	2	7.51	472	6.7	<5	1.96	2	33	144	1993	5.69	1.79	1.43	460	<2	3.19	62	645	17	206	0.31	102	11	230

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2805RR

Date : Nov-28-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
44809	<1	0.51	38	6.0	<5	0.80	2	102	1949	1	5.82	0.07	23.96	1111	<2	0.05	2248	48	25	48	0.03	31	<10	42
44810	<1	0.16	<10	5.4	<5	0.25	2	103	1861	14	5.60	0.02	24.35	802	<2	0.02	2266	23	16	24	<0.01	16	<10	35
44811	<1	0.12	<10	5.2	<5	0.68	2	93	1340	21	5.31	0.02	22.97	741	<2	0.02	2112	19	18	36	<0.01	15	<10	23
44812	<1	0.13	<10	5.0	<5	0.18	2	95	1386	23	5.27	0.03	23.71	750	<2	0.02	2171	23	24	21	<0.01	14	<10	22
44813	<1	0.12	<10	5.4	<5	<0.01	2	99	1596	8	5.65	0.02	23.85	738	<2	0.02	2281	18	17	7	<0.01	14	<10	23
44814	<1	0.11	96	5.5	<5	0.07	2	104	1442	6	5.68	0.04	24.52	771	<2	0.02	2224	21	20	19	<0.01	15	<10	23
44815	<1	0.09	33	5.3	<5	0.07	2	97	1461	6	5.51	0.02	24.17	791	<2	0.02	2094	21	19	24	<0.01	12	<10	23
44816	<1	0.06	70	5.4	<5	0.34	2	98	1248	<1	5.62	0.01	24.02	798	<2	0.01	2140	42	17	36	<0.01	12	<10	23
44817	<1	0.07	61	5.7	<5	<0.01	2	104	1641	2	5.98	0.02	24.66	800	<2	0.01	2290	26	17	16	<0.01	13	<10	24
44818	<1	0.09	49	5.7	<5	<0.01	2	103	1865	2	5.94	0.01	24.75	794	<2	0.01	2252	23	18	16	<0.01	14	<10	24
44819	<1	0.10	72	6.0	<5	0.49	2	106	2145	1	6.10	0.01	23.58	948	<2	0.02	2304	18	14	51	<0.01	12	10	23
44820	<1	5.07	84	6.7	<5	0.21	1	82	1344	1	6.59	0.17	16.98	962	<2	0.16	1310	516	6	52	0.21	147	11	79
44821	<1	0.10	94	5.4	<5	0.45	2	99	1216	6	5.64	0.03	24.00	913	<2	0.02	2232	21	19	53	<0.01	14	<10	27
44822	<1	0.09	82	5.6	<5	<0.01	2	103	1466	6	5.81	0.02	24.22	919	<2	0.01	2191	15	40	19	<0.01	13	<10	30
44823	<1	0.15	15	5.8	<5	0.25	2	107	1507	56	5.91	0.04	23.32	748	<2	0.01	2090	32	16	34	0.01	17	<10	23
44824	<1	0.11	78	5.4	<5	<0.01	2	108	1412	8	5.64	0.01	23.58	789	<2	0.01	2091	16	23	11	<0.01	15	<10	18
44825	<1	0.09	47	5.8	<5	<0.01	2	104	1389	9	5.95	0.02	23.93	701	<2	0.02	2226	28	20	4	<0.01	14	10	18
44826	<1	0.09	40	6.0	<5	<0.01	2	104	1726	7	6.13	0.04	24.18	677	<2	0.01	2266	20	17	6	<0.01	13	<10	18
44827	<1	0.37	46	6.3	<5	1.39	2	109	2002	6	6.40	0.03	23.41	786	<2	0.02	2183	39	20	86	0.01	19	10	23
44828	<1	8.50	989	5.6	<5	0.05	<1	30	223	<1	5.26	2.42	6.25	636	<2	2.85	147	858	<2	231	0.31	167	<10	67
44829	<1	9.03	712	6.2	<5	0.19	<1	27	47	<1	5.62	2.23	6.00	746	<2	3.23	28	889	<2	334	0.39	182	10	87
44830	<1	1.01	43	5.5	<5	1.43	2	90	1567	94	5.49	0.09	20.30	786	<2	0.07	1817	105	16	123	0.04	32	<10	32
44831	<1	3.19	335	6.0	<5	0.24	1	77	1159	<1	6.05	0.38	19.49	768	<2	0.39	1428	364	9	201	0.17	102	<10	32
44832	<1	0.14	81	5.3	<5	0.08	2	106	1446	7	5.43	0.01	23.25	636	<2	0.03	2295	20	14	24	<0.01	16	<10	18
44833	<1	0.90	22	4.9	<5	2.01	2	78	1255	10	4.85	0.02	18.91	607	2	0.02	1683	86	48	262	0.05	38	<10	41
44834	1	0.11	<10	5.7	<5	0.45	2	98	1460	1	5.88	0.01	24.14	866	<2	0.01	2291	17	24	25	<0.01	16	<10	28
44835	<1	0.44	191	6.2	<5	0.88	2	102	1964	5	6.19	0.03	23.76	753	<2	0.02	2158	46	21	74	0.02	27	11	33
44836	<1	0.10	97	5.7	<5	0.06	2	105	1394	<1	5.79	0.03	24.40	688	<2	0.01	2241	23	19	50	<0.01	18	<10	19
44837	1	0.07	58	7.3	<5	0.08	2	105	1446	4	6.43	0.05	23.88	733	<2	0.02	2152	18	20	35	<0.01	16	<10	19
44838	<1	0.08	53	5.5	<5	0.39	2	104	1151	<1	5.61	0.06	23.99	684	<2	0.01	2258	16	18	46	<0.01	14	10	16

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2805RR

Date : Nov-28-08

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
44839	<1	0.11	62	7.1	<5	0.33	3	100	1118	<1	6.96	0.07	22.54	592	<2	0.01	2148	12	29	25	<0.01	21	11	18
44840	<1	0.08	65	5.9	<5	0.69	2	107	1181	<1	6.09	0.02	24.79	785	<2	0.01	2335	18	19	46	<0.01	16	<10	17
44841	<1	0.07	69	5.6	<5	1.34	2	111	960	<1	5.78	0.01	23.01	742	<2	0.01	2293	10	19	147	<0.01	16	<10	15
44842	<1	2.86	73	7.2	<5	0.86	2	84	727	7	7.02	0.01	20.68	806	<2	0.02	1445	300	27	87	0.14	104	<10	29
44843	<1	0.14	<10	5.0	<5	2.23	2	90	1053	7	4.92	0.01	21.94	1194	<2	0.02	1933	13	17	286	<0.01	19	<10	22
44844	<1	0.16	<10	5.5	<5	0.02	2	102	1276	<1	5.64	0.01	24.27	668	<2	0.01	2175	17	18	28	<0.01	20	<10	19
44845	<1	0.07	31	6.8	<5	<0.01	3	117	1577	<1	7.01	0.08	27.49	865	<2	0.01	2620	10	21	8	<0.01	15	<10	22
44846	<1	0.09	11	5.5	<5	<0.01	2	98	1219	3	5.53	0.01	22.84	815	<2	0.01	2112	12	21	12	<0.01	16	<10	21
44847	<1	0.35	24	5.0	<5	0.20	2	92	1352	10	4.89	0.01	21.62	1119	<2	0.01	1889	33	22	44	0.01	23	<10	42
44848	<1	0.30	15	5.5	<5	0.22	2	98	1316	2	5.39	0.01	22.56	824	<2	0.01	2054	22	22	27	0.01	25	<10	40
44849	<1	0.16	<10	6.7	<5	1.97	2	100	2041	<1	6.61	0.01	21.98	718	<2	0.02	2121	18	22	68	<0.01	21	<10	27
44850	<1	2.42	70	4.9	<5	4.70	1	68	845	19	4.78	0.10	15.10	1275	<2	0.34	1383	286	16	270	0.08	63	<10	53
44851	<1	8.03	378	6.7	<5	2.13	1	49	270	42	6.19	0.96	7.50	2077	<2	2.36	358	841	72	336	0.33	196	<10	128
44852	<1	3.15	524	6.0	<5	1.57	1	85	1137	7	5.14	1.31	16.35	1140	<2	0.93	1446	483	21	331	0.16	71	<10	61
44853	<1	6.50	1156	6.1	<5	5.29	1	49	476	20	4.95	2.57	5.85	1400	<2	1.64	570	1277	23	748	0.39	163	<10	79
44854	<1	6.24	968	6.9	<5	4.35	1	60	879	5	6.11	1.88	9.69	1893	<2	0.94	647	1275	35	480	0.41	184	<10	103
44855	<1	0.21	53	4.8	<5	3.57	2	95	2178	<1	4.78	0.02	19.92	897	<2	0.02	2012	16	15	116	0.01	18	<10	42
44856	<1	0.15	107	5.7	<5	1.13	2	107	1944	<1	5.83	0.01	22.86	872	<2	0.01	2163	17	19	91	<0.01	19	<10	36
44857	<1	0.12	<10	5.1	<5	2.28	2	103	1411	<1	5.24	<0.01	22.01	1078	<2	0.01	2026	25	11	143	<0.01	16	<10	15
44858	1	0.14	<10	5.4	<5	1.09	2	108	1630	<1	5.64	<0.01	23.37	908	<2	0.01	2179	20	14	60	<0.01	20	<10	13
44859	<1	0.10	12	6.0	<5	0.53	2	112	1568	<1	6.05	<0.01	24.24	884	<2	0.01	2364	18	17	31	<0.01	19	<10	16
44860	<1	0.10	31	5.7	<5	1.11	2	106	1427	<1	5.81	0.01	23.43	893	<2	0.01	2221	18	30	45	<0.01	18	<10	21
44861	<1	0.09	<10	5.6	<5	2.08	2	103	1216	<1	5.68	<0.01	22.59	978	<2	0.01	2166	18	12	152	<0.01	18	<10	14
44862	<1	9.12	344	8.1	<5	0.09	1	52	513	80	7.78	1.50	11.37	1361	<2	1.66	369	998	<2	204	0.45	271	<10	69
44863	<1	2.38	109	5.7	<5	4.93	2	79	977	<1	5.52	0.39	15.80	996	<2	0.07	1298	258	7	228	0.10	90	<10	34
44864	<1	0.16	<10	5.0	<5	3.97	2	96	1727	20	5.09	0.01	18.79	869	<2	0.03	2047	23	47	225	<0.01	17	<10	130
44865	<1	0.34	<10	4.5	<5	3.92	2	86	1272	<1	4.64	0.01	18.96	747	<2	0.03	1800	45	11	408	0.01	25	<10	19
44866	<1	0.20	<10	5.6	<5	2.42	2	108	2026	<1	5.59	0.01	24.52	1040	<2	0.02	2260	18	12	186	<0.01	19	<10	22
44867	<1	0.19	<10	5.0	<5	1.95	2	99	1847	<1	5.18	<0.01	22.97	870	<2	0.02	2034	<10	13	103	<0.01	22	<10	20
44868	<1	7.43	1579	7.6	<5	3.20	1	44	301	14	6.24	2.90	6.41	1057	<2	1.63	193	2215	11	956	0.55	183	<10	65

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2805RR

Date : Nov-28-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
44869	2	6.34	1528	7.7	<5	3.33	1	52	486	9	6.12	2.84	7.58	1104	<2	1.65	495	1935	13	867	0.47	151	<10	73
44870	<1	0.61	106	5.6	<5	0.54	2	98	1254	<1	5.38	0.23	21.91	796	<2	0.14	2056	179	12	101	0.04	30	<10	65
44871	<1	0.20	10	6.0	<5	0.69	2	106	1420	2	5.81	0.01	23.01	960	<2	0.02	2211	39	13	61	0.01	23	<10	34
44872	<1	1.31	113	5.7	<5	4.18	2	81	1125	9	5.24	0.26	16.90	1396	<2	0.22	1674	250	91	265	0.08	47	<10	56
44873	<1	3.07	785	6.6	<5	3.00	2	79	653	<1	5.81	1.02	15.44	1932	<2	0.67	1384	974	56	736	0.23	77	<10	73
44874	<1	0.07	<10	5.2	<5	0.67	2	103	1003	<1	5.17	<0.01	22.98	925	<2	0.01	2175	27	14	106	<0.01	13	<10	15
44875	<1	0.10	10	5.0	<5	0.56	2	103	1099	<1	5.09	<0.01	23.47	885	<2	0.01	2249	24	12	58	<0.01	14	<10	8
44876	<1	0.11	18	5.7	<5	<0.01	2	111	1934	<1	5.63	<0.01	24.33	790	<2	0.01	2615	26	20	38	<0.01	13	<10	13
44877	<1	0.15	56	5.7	<5	0.51	2	107	1994	<1	5.82	0.01	24.74	915	<2	0.01	2293	23	37	77	0.01	15	<10	29
44878	<1	0.12	<10	5.2	<5	0.20	2	110	1325	<1	5.32	<0.01	25.38	875	<2	0.01	2391	18	13	14	<0.01	17	<10	8
44879	<1	0.49	<10	5.4	<5	1.14	2	103	1313	<1	5.48	<0.01	23.33	830	<2	0.02	2101	61	17	72	0.03	32	<10	8
44880	<1	0.14	<10	5.0	<5	0.61	2	100	1335	<1	5.16	<0.01	24.36	853	<2	0.01	2145	14	12	40	<0.01	18	<10	6
44881	<1	0.16	<10	5.5	<5	0.81	2	106	1233	<1	5.31	0.01	23.86	874	<2	0.02	2003	23	9	48	0.01	18	<10	19
44882	<1	0.56	12	6.3	<5	1.18	2	111	1812	<1	6.14	0.02	23.38	995	<2	0.03	1970	47	17	90	0.03	37	<10	44
44883	<1	0.13	<10	6.3	<5	0.66	2	108	1644	<1	5.97	<0.01	25.37	943	<2	0.02	2065	25	10	35	<0.01	18	<10	31
44884	<1	0.13	<10	6.3	<5	0.66	2	104	1709	<1	5.89	<0.01	24.34	938	<2	0.01	1908	18	14	65	<0.01	17	<10	33
44885	<1	0.15	13	5.5	<5	0.17	2	108	1385	<1	5.52	0.01	25.28	843	<2	0.02	2141	22	12	82	<0.01	18	<10	26
44886	<1	0.15	<10	6.0	<5	0.28	2	105	1403	<1	5.76	0.01	24.76	819	<2	0.02	2036	19	10	87	<0.01	19	<10	23
44887	<1	0.13	<10	5.5	<5	0.87	2	103	1292	<1	5.44	<0.01	24.30	785	<2	0.02	2050	18	9	104	<0.01	17	<10	21
44888	<1	0.09	<10	5.4	<5	0.81	2	117	1287	<1	5.10	<0.01	24.89	1037	<2	0.01	2230	16	11	58	<0.01	13	<10	31
44889	<1	6.95	1649	7.4	<5	4.01	1	44	360	11	5.88	2.69	5.33	1130	<2	2.11	203	2242	6	873	0.52	163	12	81
44890	<1	8.07	2414	8.3	<5	4.27	1	42	203	2	6.36	3.06	3.99	1130	<2	2.21	42	2615	7	1273	0.60	189	10	77
44891	<1	3.98	699	7.2	<5	2.25	2	80	1014	3	6.40	1.01	14.83	1185	21	0.61	1063	989	63	687	0.27	108	<10	85
44892	<1	0.10	<10	5.3	<5	0.91	2	108	1543	2	5.08	0.01	23.39	1895	<2	0.02	1906	23	19	42	<0.01	14	<10	33
44893	<1	0.10	<10	5.7	<5	0.38	2	114	1499	<1	5.45	0.01	25.08	869	<2	0.02	2059	15	13	33	<0.01	16	<10	23
44894	<1	0.09	<10	6.5	<5	0.62	2	114	1783	<1	6.07	<0.01	24.17	911	2	0.01	1966	10	11	39	<0.01	16	<10	21
44895	<1	0.16	<10	6.2	<5	0.22	2	111	1700	<1	5.93	<0.01	24.32	699	<2	0.02	1947	16	11	27	<0.01	19	<10	18
44896	<1	0.10	<10	6.3	<5	0.26	2	112	1761	<1	5.75	<0.01	24.94	741	<2	0.02	2169	16	10	29	<0.01	16	<10	25
44897	<1	0.07	<10	6.0	<5	0.63	2	110	1419	<1	5.78	<0.01	24.08	823	<2	0.02	1983	20	12	58	<0.01	14	<10	25
44898	<1	0.07	<10	6.0	<5	0.72	2	108	1050	<1	5.86	<0.01	24.76	874	<2	0.01	1931	15	17	52	<0.01	14	<10	20

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2805RR

Date : Nov-28-08

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
44899	<1	0.12	<10	5.9	<5	0.43	2	112	2172	<1	5.52	0.01	24.68	676	<2	0.02	2017	15	12	45	<0.01	15	<10	29
44900	<1	0.09	<10	6.0	<5	0.42	2	109	1882	<1	5.71	<0.01	25.18	788	<2	0.02	1939	13	12	50	<0.01	17	<10	27
Duplicates:																								
44809	<1	0.47	10	5.5	<5	0.55	2	101	1923	2	5.66	0.11	23.49	1080	<2	0.04	2140	47	30	41	0.02	28	<10	44
44818	<1	0.09	107	5.9	<5	<0.01	2	104	1849	<1	6.08	0.01	25.21	813	<2	0.01	2308	20	17	16	<0.01	15	10	24
44828	<1	8.37	869	5.7	<5	0.04	<1	30	224	<1	5.19	2.38	6.14	627	<2	2.81	150	886	<2	226	0.30	166	<10	66
44833	<1	0.87	58	4.9	<5	1.98	2	76	1211	5	4.81	0.06	18.80	600	3	0.02	1631	91	44	258	0.05	38	10	38
44842	<1	2.92	123	7.3	<5	0.88	2	86	710	8	7.07	0.04	21.09	830	<2	0.01	1465	320	27	90	0.16	108	<10	29
44852	<1	3.08	519	5.8	<5	1.51	1	84	1086	8	4.97	1.43	15.93	1101	<2	0.88	1401	499	20	323	0.15	69	<10	61
44857	<1	0.13	<10	5.2	<5	2.32	2	104	1718	<1	5.34	<0.01	22.49	1105	<2	0.01	2067	20	10	142	<0.01	17	<10	18
44866	<1	0.18	<10	5.3	<5	2.24	2	99	1886	<1	5.21	<0.01	23.16	972	<2	0.02	2098	12	14	175	<0.01	19	<10	16
44876	<1	0.10	40	5.6	<5	<0.01	2	109	1658	<1	5.54	<0.01	24.30	776	<2	0.01	2566	25	30	37	<0.01	15	<10	18
44881	<1	0.16	11	5.6	<5	0.82	2	108	1250	<1	5.32	0.01	24.05	876	<2	0.02	1988	28	15	48	0.01	18	<10	19
44890	<1	8.07	2440	8.3	<5	4.27	1	41	203	2	6.33	3.06	4.01	1130	<2	2.21	42	2552	6	1262	0.60	189	<10	77
44900	<1	0.10	10	6.0	<5	0.43	2	108	1488	<1	5.68	0.01	25.07	784	<2	0.02	1927	19	12	52	<0.01	17	<10	23
Standards:																								
Blank	<1	<0.01	<10	<0.5	<5	<0.01	<1	1	1	<1	0.01	<0.01	0.01	<5	<2	0.01	3	<10	<2	<1	<0.01	<1	<10	<2
CH-4	2	7.33	457	6.2	<5	1.62	1	30	128	1996	5.39	1.75	1.39	447	2	2.96	57	649	13	195	0.31	97	<10	203

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2905RR

Date : Sep-18-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
44901	<1	0.09	11	6.1	<5	0.22	2	112	1585	<1	5.97	0.01	24.67	761	<2	0.02	2371	21	12	37	<0.01	15	<10	21
44902	<1	0.06	<10	5.7	<5	0.74	2	108	1126	<1	5.50	0.01	25.45	845	<2	0.02	2259	16	11	68	<0.01	13	<10	24
44903	<1	0.08	<10	6.5	<5	0.52	2	117	1417	<1	6.09	0.01	26.42	962	<2	0.01	2591	16	12	31	<0.01	16	<10	23
44904	<1	0.08	<10	6.8	<5	0.91	2	120	1065	<1	6.50	0.01	27.12	1026	<2	0.01	2525	19	14	32	<0.01	19	<10	21
44905	<1	0.07	15	5.9	<5	0.08	2	110	1249	<1	5.56	<0.01	24.75	773	<2	0.01	2311	13	12	5	<0.01	16	<10	22
44906	<1	0.86	<10	6.6	<5	0.78	2	109	967	<1	6.22	0.01	22.49	793	<2	0.02	2143	119	13	40	0.03	26	<10	20
44907	<1	0.03	<10	6.3	<5	0.38	2	122	731	<1	5.81	<0.01	25.44	912	<2	0.01	2433	13	11	5	<0.01	13	<10	23
44925	<1	0.97	28	6.6	<5	2.21	2	105	1626	<1	5.82	0.10	22.77	999	<2	0.05	2059	106	10	192	0.04	46	<10	70
44926	<1	0.17	11	6.4	<5	0.29	2	105	1164	2	5.60	0.01	24.68	844	<2	0.01	2270	27	10	28	<0.01	23	<10	45
44927	<1	0.54	124	7.3	<5	1.08	2	105	1939	2	6.28	0.05	23.93	1075	<2	0.02	2179	238	49	96	0.04	37	<10	65
44928	<1	0.30	57	6.1	<5	0.29	2	111	1152	<1	5.56	0.08	25.11	1001	<2	0.02	2322	159	22	71	0.03	25	<10	101
44929	<1	0.13	<10	5.7	<5	0.58	2	102	1301	2	5.35	0.01	22.91	1021	<2	0.02	2153	42	14	62	<0.01	18	<10	48
44930	<1	7.06	1404	8.1	<5	2.67	1	36	222	14	6.28	2.58	4.62	2371	<2	1.07	178	1969	26	596	0.44	150	<10	187
44931	<1	7.82	1779	8.6	<5	2.55	2	32	121	20	6.38	3.42	2.99	2837	<2	1.04	29	2021	82	695	0.50	162	<10	481
44932	1	7.17	1340	11.0	<5	2.07	3	33	131	18	8.77	2.16	3.32	4218	<2	0.73	24	1952	490	440	0.36	156	<10	603
45001	<1	0.54	130	6.3	<5	0.80	2	103	1656	<1	5.74	0.25	22.39	934	<2	0.11	2115	177	15	98	0.04	23	<10	45
45002	<1	0.10	<10	6.0	<5	1.20	2	100	1717	<1	5.31	0.01	22.90	999	<2	0.01	2213	23	30	98	<0.01	17	11	37
45013	<1	1.76	26	5.7	<5	10.36	1	60	992	<1	4.44	0.02	13.18	2265	<2	0.02	1214	457	25	368	0.09	44	<10	143
45014	<1	0.14	10	5.7	<5	3.27	2	108	1766	<1	5.44	0.02	22.18	996	<2	0.02	2275	47	16	139	0.01	15	<10	40
45015	<1	0.11	16	5.9	<5	2.40	2	111	1905	<1	5.65	0.03	22.73	968	<2	0.02	2308	37	43	46	0.01	15	<10	33
45016	<1	0.09	<10	5.6	<5	1.06	2	111	1438	<1	5.48	0.01	22.99	828	<2	0.01	2295	17	49	23	<0.01	16	<10	28
45017	<1	0.12	14	5.5	<5	1.76	2	106	1785	<1	5.30	0.02	20.93	928	<2	0.02	1992	18	16	477	<0.01	14	<10	37
45018	<1	0.16	11	5.6	<5	6.59	2	98	1228	<1	5.07	0.01	16.69	1192	<2	0.03	1838	33	7	330	0.01	16	<10	26
45019	<1	0.29	<10	4.5	<5	3.55	2	92	957	<1	4.30	<0.01	19.40	1364	<2	0.02	1668	22	11	1349	<0.01	19	<10	52
45020	<1	0.11	<10	6.3	<5	0.58	2	110	1511	<1	6.05	<0.01	22.62	764	<2	0.02	1990	<10	12	889	<0.01	18	13	27
45021	<1	0.26	<10	5.6	<5	0.81	2	100	1229	<1	5.47	<0.01	22.13	1181	<2	0.01	1807	58	32	107	0.01	18	<10	66
45022	<1	0.07	<10	5.1	<5	0.10	2	108	913	<1	5.09	<0.01	24.31	788	<2	0.01	2043	<10	13	20	<0.01	15	<10	22
45023	<1	0.08	<10	5.3	<5	0.17	2	105	1033	<1	5.19	<0.01	24.70	747	<2	0.01	1958	<10	13	12	<0.01	15	<10	22
45024	<1	0.15	<10	5.3	<5	0.41	2	101	916	<1	5.13	<0.01	23.41	774	<2	0.01	1895	24	9	29	<0.01	18	<10	28
45025	<1	0.15	<10	5.3	<5	0.45	2	101	1143	<1	5.12	0.02	23.46	712	<2	0.06	1821	15	9	11	<0.01	18	<10	23

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2905RR

Date : Sep-18-08

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
45026	<1	0.12	<10	5.2	<5	0.48	2	102	1005	<1	5.00	<0.01	23.06	754	<2	0.02	1883	16	10	11	<0.01	19	<10	23
45027	<1	0.08	<10	5.1	<5	0.39	2	102	1113	<1	4.95	<0.01	23.80	749	<2	0.01	1885	<10	11	9	<0.01	15	<10	22
45028	<1	0.09	<10	6.0	<5	0.42	2	100	1671	<1	5.82	<0.01	24.01	721	<2	0.02	1706	<10	10	9	<0.01	17	<10	23
45029	<1	0.09	<10	5.5	<5	0.22	2	107	1300	<1	5.26	<0.01	24.06	752	<2	0.02	2061	<10	11	7	<0.01	16	<10	27
45030	<1	0.07	11	6.5	<5	0.86	2	105	1363	<1	6.25	<0.01	23.48	837	<2	0.02	1899	<10	11	10	<0.01	18	<10	23
45031	<1	0.06	<10	5.9	<5	0.14	2	106	1225	<1	5.61	<0.01	24.33	746	<2	0.02	2002	<10	10	5	<0.01	14	<10	20
45032	<1	0.07	<10	5.8	<5	0.11	2	106	1160	<1	5.57	<0.01	24.03	727	<2	0.02	1991	<10	9	4	<0.01	15	<10	19
45033	<1	0.08	<10	5.1	<5	0.25	2	101	995	<1	5.10	<0.01	23.05	712	<2	0.02	1937	<10	9	4	<0.01	15	<10	17
45034	<1	0.09	<10	5.3	<5	0.19	2	103	934	<1	5.18	<0.01	23.22	679	<2	0.02	1924	<10	8	3	<0.01	17	<10	16
45035	<1	0.16	<10	5.7	<5	0.24	2	108	1143	<1	5.57	<0.01	25.50	749	<2	0.03	1989	<10	4	3	<0.01	23	<10	21
45036	<1	0.08	<10	5.6	<5	0.10	2	109	1403	<1	5.41	<0.01	24.40	786	<2	0.01	1900	<10	10	5	<0.01	15	<10	24
45037	<1	0.08	<10	5.9	<5	0.30	2	115	1473	<1	5.73	<0.01	24.46	868	<2	0.02	2009	<10	15	11	<0.01	15	<10	41
45038	<1	0.08	<10	5.5	<5	0.28	2	105	1195	<1	5.27	<0.01	23.80	817	<2	0.02	1990	<10	21	7	<0.01	15	<10	98
45039	<1	0.08	<10	4.2	<5	0.11	2	96	937	5	4.78	0.01	22.84	645	<2	0.02	2064	21	13	3	<0.01	14	<10	19
45040	<1	0.07	<10	4.8	<5	0.11	2	96	1482	<1	5.19	<0.01	22.98	730	<2	0.01	1911	29	10	4	<0.01	13	<10	19
45041	<1	0.06	<10	4.1	<5	0.08	2	98	1329	<1	4.74	<0.01	24.12	771	<2	0.01	2173	14	9	4	<0.01	11	<10	20
45042	<1	0.05	<10	4.9	<5	0.05	2	103	1263	<1	5.30	<0.01	24.67	753	<2	0.01	2243	29	11	2	<0.01	11	14	18
45043	<1	0.05	<10	4.6	<5	0.04	2	108	1525	<1	5.21	<0.01	24.44	785	<2	0.01	2298	36	8	2	<0.01	10	12	19
45044	<1	0.04	<10	4.3	<5	0.04	2	110	1072	<1	4.85	<0.01	24.92	777	<2	0.01	2338	10	10	2	<0.01	9	14	18
45045	<1	0.03	<10	4.7	<5	0.05	2	111	1141	<1	5.26	<0.01	24.74	806	<2	0.01	2393	34	10	3	<0.01	10	<10	17
45046	<1	0.04	<10	4.5	<5	0.05	2	105	1193	<1	5.25	<0.01	24.27	838	<2	0.01	2261	25	5	2	<0.01	10	10	20
45047	<1	0.03	<10	3.9	<5	0.14	2	110	931	<1	4.64	<0.01	25.36	847	<2	0.01	2315	28	8	4	<0.01	9	13	19
45048	<1	0.04	<10	3.7	<5	0.11	2	111	817	<1	4.18	<0.01	25.38	830	<2	0.01	2334	28	7	4	<0.01	9	12	19
45049	<1	0.05	<10	4.7	<5	0.07	2	115	1513	<1	5.33	<0.01	24.96	847	<2	0.01	2346	23	6	3	<0.01	10	11	17
45050	<1	0.05	<10	4.8	<5	0.05	2	119	1450	<1	5.49	<0.01	25.28	858	<2	0.01	2347	34	7	2	<0.01	10	11	21
45051	<1	0.04	<10	4.7	<5	0.08	2	120	1181	<1	5.23	<0.01	25.77	845	<2	0.01	2441	35	13	4	<0.01	11	<10	18
45052	<1	0.05	<10	4.6	<5	0.07	2	119	1245	<1	5.27	<0.01	24.86	785	<2	0.01	2429	25	5	3	<0.01	10	11	18
45053	<1	0.04	<10	4.8	<5	0.06	2	118	1549	<1	5.40	<0.01	25.22	854	<2	0.01	2401	34	3	3	<0.01	9	12	18
45054	<1	0.04	<10	3.8	<5	0.05	2	121	1353	<1	4.57	0.01	26.69	822	<2	0.01	2696	37	7	3	<0.01	9	<10	20
45055	<1	0.04	10	4.4	<5	0.10	2	121	1469	<1	4.87	<0.01	25.41	856	<2	0.01	2441	24	10	4	<0.01	9	<10	17

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2905RR

Date : Sep-18-08

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
45056	<1	0.05	12	4.1	<5	0.10	2	115	1408	<1	4.53	<0.01	24.98	857	<2	0.01	2423	30	5	4	<0.01	8	<10	20
45057	<1	0.05	<10	4.0	<5	0.13	2	110	1468	<1	4.71	<0.01	25.62	917	<2	0.01	2351	23	8	6	<0.01	8	12	18
45058	<1	0.05	<10	4.4	<5	0.18	2	115	2011	<1	5.09	<0.01	25.73	963	<2	0.01	2327	32	4	8	<0.01	8	11	22
45059	<1	0.05	<10	4.6	<5	0.11	2	116	1555	<1	5.19	0.01	24.93	842	<2	0.01	2460	38	13	4	<0.01	9	16	20
45060	<1	0.04	<10	4.3	<5	0.04	2	113	1306	<1	4.89	<0.01	24.11	784	<2	0.01	2325	26	7	2	<0.01	10	14	17
45061	<1	0.04	<10	5.1	<5	0.09	2	108	1505	<1	5.61	0.01	24.09	828	<2	0.01	2104	43	10	3	<0.01	10	21	18
45062	<1	0.04	<10	4.6	<5	0.15	2	111	1818	<1	5.06	<0.01	23.95	877	<2	0.01	2192	17	2	5	<0.01	9	15	20
45063	<1	0.06	<10	4.8	<5	0.03	2	115	1935	<1	5.59	0.01	23.43	805	<2	0.01	2247	26	8	2	<0.01	10	19	23
45064	<1	0.06	<10	4.1	<5	0.19	2	106	1539	<1	4.71	<0.01	23.17	779	<2	0.01	2016	32	7	6	<0.01	8	16	19
45065	1	0.08	<10	4.3	<5	0.16	2	102	1791	<1	4.93	0.01	22.79	757	<2	0.02	1973	37	5	2	<0.01	10	12	17
45066	<1	0.15	<10	4.5	<5	0.18	2	105	1122	<1	4.99	0.06	22.84	771	<2	0.01	2168	64	9	7	0.01	12	15	20
45068	<1	0.22	27	4.7	<5	0.35	2	98	1642	<1	5.29	0.06	22.74	886	<2	0.03	2008	84	4	16	0.01	14	12	25
45069	<1	0.06	<10	4.5	<5	0.24	2	95	1124	<1	5.03	0.01	22.81	804	<2	0.01	2008	31	6	3	<0.01	11	12	20
45070	<1	0.15	29	4.9	<5	0.12	2	100	836	<1	5.39	0.06	22.67	739	<2	0.04	2178	88	8	14	0.01	15	10	19
45071	<1	0.06	<10	4.2	<5	0.06	2	94	832	<1	4.74	0.01	23.14	705	<2	0.01	2017	16	8	2	<0.01	12	20	20
45072	<1	0.05	<10	4.6	<5	0.05	2	96	784	<1	5.07	<0.01	23.24	694	<2	0.01	2099	25	8	2	<0.01	12	11	18
45073	<1	0.05	<10	4.5	<5	0.11	2	102	783	<1	5.09	<0.01	24.28	780	<2	0.01	2206	32	8	2	<0.01	12	10	22
45074	<1	0.09	<10	4.5	<5	0.16	2	101	906	<1	5.08	<0.01	23.66	721	<2	0.01	2153	38	13	3	<0.01	14	15	21
45075	<1	0.09	<10	4.5	<5	0.12	2	98	1210	<1	5.08	<0.01	23.08	713	<2	0.01	2069	30	10	2	<0.01	14	16	21
45076	<1	0.07	<10	4.2	<5	0.28	2	103	1198	6	4.82	0.01	23.93	755	<2	0.01	2209	28	6	5	<0.01	11	13	19
45077	<1	0.08	<10	4.5	<5	0.17	2	108	1075	<1	5.12	0.01	24.36	735	<2	0.01	2275	37	5	2	<0.01	15	13	21
45078	<1	0.08	<10	4.4	<5	0.06	2	102	1011	<1	5.08	<0.01	23.63	698	<2	0.01	2111	31	6	1	<0.01	14	15	19
45079	<1	0.10	<10	4.4	<5	0.05	2	100	1074	<1	5.04	<0.01	23.25	726	<2	0.01	2077	40	5	1	<0.01	16	12	22
45080	<1	0.11	<10	4.2	<5	0.04	2	97	1129	2	4.86	0.01	23.16	701	<2	0.02	2024	26	3	1	<0.01	14	13	20
45081	<1	0.04	<10	4.1	<5	0.19	2	107	901	1	4.69	0.01	24.22	795	<2	0.01	2135	36	8	2	<0.01	10	13	20
45082	<1	0.04	<10	3.9	<5	0.68	2	108	797	4	4.35	<0.01	24.29	751	<2	0.01	2210	34	7	360	<0.01	8	12	18
45083	<1	0.08	<10	5.0	<5	0.08	3	125	1241	8	5.56	<0.01	27.14	907	<2	0.01	2568	32	18	1	<0.01	12	13	24
45084	<1	0.09	<10	4.9	<5	0.01	2	111	1088	4	5.52	<0.01	25.05	808	<2	0.01	2248	23	12	1	<0.01	14	<10	21
45085	<1	0.10	<10	4.9	<5	0.01	3	108	1031	8	5.49	<0.01	24.65	779	<2	0.01	2229	<10	20	1	<0.01	16	<10	20
45086	<1	0.11	<10	4.7	<5	0.04	2	106	1032	3	5.27	<0.01	24.61	751	<2	0.02	2204	22	15	1	<0.01	17	<10	20

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2905RR

Date : Sep-18-08

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
45087	<1	0.10	<10	4.7	<5	0.11	2	108	1019	<1	5.23	<0.01	24.75	771	<2	0.01	2249	23	11	4	<0.01	16	10	18
45088	<1	0.12	<10	4.6	<5	0.09	2	108	1088	<1	5.17	0.01	24.46	751	<2	0.01	2137	11	11	3	<0.01	17	12	20
45089	<1	0.08	<10	4.5	<5	0.47	2	110	1156	<1	5.19	<0.01	24.40	799	<2	0.01	2194	19	13	2	<0.01	15	12	21
45090	1	0.06	<10	4.8	<5	0.13	2	118	1191	<1	5.45	0.01	25.07	843	<2	0.01	2199	23	14	3	<0.01	14	12	21
45091	<1	0.08	<10	4.5	<5	0.08	2	111	1091	2	4.91	<0.01	24.20	832	<2	0.01	2092	12	14	15	<0.01	15	<10	21
45092	1	0.10	<10	5.0	<5	0.04	3	116	1445	<1	5.67	<0.01	24.10	889	<2	0.01	2067	18	15	1	<0.01	15	<10	27
45093	<1	0.10	<10	5.0	<5	0.03	3	113	1233	<1	5.63	<0.01	24.39	801	<2	0.01	2222	21	15	1	<0.01	17	15	24
45094	<1	0.14	<10	5.2	<5	0.04	3	120	1331	<1	5.85	0.01	24.43	849	<2	0.01	2147	15	16	1	<0.01	19	<10	26
45095	<1	0.11	<10	5.6	<5	0.08	3	114	1389	<1	6.24	<0.01	24.13	797	<2	0.01	2147	24	14	2	<0.01	19	14	21
45096	<1	0.11	<10	4.4	<5	1.89	2	87	1943	<1	4.93	<0.01	20.83	817	<2	0.01	1909	21	13	93	<0.01	13	<10	25
45097	<1	0.06	<10	4.3	<5	1.40	2	97	1362	<1	4.83	<0.01	22.67	791	<2	0.01	2102	17	8	75	<0.01	12	<10	19
45098	<1	3.28	41	6.3	<5	0.74	2	87	1125	82	6.84	0.09	20.37	922	<2	0.08	1435	345	11	84	0.17	126	<10	39
45099	<1	0.14	<10	4.9	<5	2.01	2	100	1667	<1	5.36	0.01	22.50	798	<2	0.01	2168	45	13	99	0.01	16	<10	21
45100	1	0.10	<10	3.9	<5	1.65	2	90	2663	<1	4.37	0.01	21.64	884	<2	0.01	2143	29	16	149	<0.01	10	11	37
Duplicates:																								
45017	<1	0.13	13	5.5	<5	1.77	2	107	1862	<1	5.30	0.01	20.97	933	<2	0.02	1984	19	18	479	<0.01	14	<10	38
45026	<1	0.11	<10	5.5	<5	0.49	2	102	1239	<1	5.33	<0.01	23.38	737	<2	0.02	1923	<10	9	11	<0.01	18	<10	21
45036	<1	0.08	<10	5.9	<5	0.11	2	113	1623	<1	5.68	<0.01	25.48	824	<2	0.01	1984	<10	11	5	<0.01	14	<10	23
45039	<1	0.07	<10	4.1	<5	0.11	2	96	1085	<1	4.77	<0.01	22.48	640	<2	0.02	2061	30	12	3	<0.01	13	<10	18
45048	<1	0.03	<10	3.6	<5	0.11	2	112	842	<1	4.11	<0.01	24.79	815	<2	0.01	2348	21	7	4	<0.01	9	11	19
45058	<1	0.05	<10	4.4	<5	0.17	2	112	1577	<1	4.96	<0.01	25.18	940	<2	0.01	2250	43	9	7	<0.01	9	14	22
45061	<1	0.05	<10	5.0	<5	0.09	2	109	1416	<1	5.54	0.01	24.19	826	<2	0.01	2083	29	6	3	<0.01	10	19	20
45070	<1	0.15	29	4.9	<5	0.12	2	99	920	<1	5.43	0.06	22.77	743	<2	0.04	2123	75	7	14	0.01	15	16	20
45080	<1	0.11	<10	4.5	<5	0.04	2	104	1083	<1	5.16	0.01	24.60	743	<2	0.01	2161	39	9	1	<0.01	15	11	22
45083	1	0.07	<10	4.5	<5	0.08	2	120	1150	2	5.31	<0.01	26.14	871	<2	0.01	2426	18	15	1	<0.01	12	<10	22
45092	1	0.52	<10	4.1	<5	0.08	1	108	1587	1	4.61	0.27	23.58	860	<2	0.61	1949	16	14	3	<0.01	14	11	25
Standards:																								
Blank	<1	0.02	<10	<0.5	<5	<0.01	<1	1	1	<1	0.02	0.01	0.01	<5	<2	0.01	1	<10	<2	<1	<0.01	1	<10	<2
CH-4	2	7.66	482	6.6	<5	1.92	2	31	132	1992	5.56	1.84	1.45	464	<2	3.05	56	732	17	205	0.32	103	<10	229

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2906RR

Date : Nov-28-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
45101	<1	0.12	<10	4.7	<5	1.75	2	104	3191	2	4.75	0.01	22.60	928	<2	0.01	2047	24	25	130	<0.01	10	<10	62
45102	<1	0.09	<10	4.8	<5	1.69	2	93	2534	1	4.66	<0.01	22.14	1108	<2	0.01	2107	25	34	178	<0.01	11	<10	75
45103	<1	0.07	<10	5.7	<5	0.81	2	108	1811	<1	5.60	<0.01	24.34	851	<2	0.01	2383	17	13	52	<0.01	13	<10	21
45104	<1	0.09	<10	5.3	<5	0.46	2	116	2786	<1	5.52	<0.01	23.98	857	<2	0.01	2385	22	12	51	<0.01	9	10	25
45105	<1	0.11	<10	5.5	<5	0.80	2	107	1828	<1	5.45	<0.01	23.72	1199	<2	0.02	2200	25	27	83	<0.01	16	<10	50
45106	<1	0.11	<10	5.8	<5	0.47	2	109	1555	2	5.80	<0.01	23.60	1541	<2	0.03	2214	15	104	31	<0.01	18	10	74
45107	<1	0.12	<10	5.3	<5	0.20	2	106	1137	<1	5.38	<0.01	24.18	933	<2	0.02	2193	19	25	22	<0.01	18	<10	29
45108	<1	0.10	<10	5.7	<5	0.13	2	114	1607	<1	5.77	<0.01	25.62	851	<2	0.02	2285	22	20	14	<0.01	16	<10	23
45109	<1	0.10	<10	5.1	<5	0.21	2	108	1967	<1	5.17	<0.01	23.70	810	<2	0.02	2306	17	13	23	<0.01	15	<10	27
45110	<1	0.09	<10	5.8	<5	0.08	2	116	2295	<1	6.05	<0.01	25.19	956	<2	0.01	2292	20	16	8	<0.01	14	10	30
45111	<1	0.09	<10	6.0	<5	0.14	2	109	2040	<1	5.87	<0.01	24.37	920	<2	0.02	2118	16	20	13	<0.01	14	11	33
45112	<1	0.10	<10	5.6	<5	0.33	2	114	2137	<1	5.70	<0.01	25.63	993	<2	0.02	2258	23	31	27	<0.01	15	<10	54
45113	<1	0.10	<10	5.2	<5	0.20	2	102	1943	<1	5.43	<0.01	24.68	896	<2	0.02	2214	18	24	9	<0.01	15	11	59
45114	<1	0.11	<10	5.9	<5	0.12	2	107	1719	<1	5.90	<0.01	25.21	896	<2	0.02	2210	27	23	6	<0.01	18	10	42
45115	<1	0.08	<10	5.4	<5	0.13	2	104	1537	1	5.56	<0.01	25.01	949	<2	0.01	2202	22	20	9	<0.01	15	<10	43
45116	<1	0.09	<10	5.0	<5	0.16	2	109	1632	1	5.13	0.01	24.79	875	<2	0.02	2213	20	30	12	<0.01	14	13	45
45117	<1	0.09	<10	4.9	<5	0.37	2	110	2051	<1	5.18	0.01	24.81	943	<2	0.01	2134	19	38	25	<0.01	13	12	56
45118	<1	0.07	<10	5.3	<5	0.38	2	115	1530	<1	5.19	<0.01	25.01	823	<2	0.01	2238	21	24	16	<0.01	14	11	39
45119	<1	0.08	<10	6.1	<5	0.04	2	118	1892	<1	6.05	<0.01	25.54	803	<2	0.01	2244	19	19	5	<0.01	14	10	35
45120	<1	0.16	<10	5.5	<5	0.19	2	116	1720	<1	5.73	0.01	25.83	862	<2	0.02	2321	27	20	17	0.01	17	13	36
45121	<1	0.11	<10	5.1	<5	0.26	2	103	1293	<1	5.14	<0.01	24.68	712	<2	0.02	2021	17	14	14	<0.01	16	<10	26
45122	<1	7.79	2510	8.6	<5	4.00	2	43	267	9	6.63	3.85	7.06	3883	<2	1.13	108	2798	493	1055	0.62	175	<10	552
45123	<1	0.19	29	5.6	<5	1.46	2	96	922	<1	5.49	0.05	23.37	965	<2	0.04	1862	45	18	67	0.01	19	<10	40
45124	<1	0.10	<10	5.6	<5	0.56	2	112	1148	<1	5.58	0.01	24.27	869	<2	0.02	2138	12	42	20	<0.01	17	<10	41
45125	<1	0.08	<10	6.5	<5	0.23	2	111	1508	<1	6.48	<0.01	24.31	849	<2	0.02	2187	12	44	15	<0.01	17	<10	49
45126	<1	0.09	<10	5.7	<5	0.03	2	111	1228	<1	5.80	<0.01	24.71	812	<2	0.02	2264	15	21	4	<0.01	17	<10	28
45127	<1	0.09	<10	5.4	<5	0.08	2	118	1130	<1	5.47	<0.01	24.76	789	<2	0.02	2258	13	20	7	<0.01	17	10	32
45128	<1	0.10	<10	6.1	<5	0.53	3	118	1214	5	6.04	<0.01	23.62	975	<2	0.02	2176	<10	288	20	<0.01	21	<10	210
45129	<1	0.15	<10	6.4	<5	0.35	2	114	1282	<1	6.59	<0.01	23.48	810	<2	0.02	2200	<10	19	15	<0.01	24	10	23
45130	<1	0.14	<10	5.6	<5	0.33	2	111	1189	<1	5.52	<0.01	24.24	773	<2	0.02	2129	<10	13	14	<0.01	22	<10	23

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2906RR

Date : Nov-28-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
45131	<1	0.12	<10	5.5	<5	0.09	2	106	844	1	5.55	<0.01	24.24	696	<2	0.02	2124	10	8	6	<0.01	22	<10	22
45132	<1	0.09	<10	5.5	<5	0.09	2	106	781	1	5.74	<0.01	23.74	690	<2	0.03	2036	10	11	4	<0.01	21	11	19
45133	<1	0.09	<10	5.3	<5	0.08	2	112	733	4	5.50	<0.01	24.73	733	<2	0.03	2221	14	15	3	<0.01	20	<10	20
45134	<1	0.08	<10	5.5	<5	0.09	2	107	866	4	5.61	<0.01	24.56	717	<2	0.03	2270	<10	15	2	<0.01	21	<10	20
45135	<1	0.11	<10	5.6	<5	0.10	2	116	985	2	5.70	<0.01	25.24	800	<2	0.03	2216	12	16	4	<0.01	20	<10	23
45136	<1	0.10	<10	5.8	<5	0.17	2	108	897	3	5.88	<0.01	24.74	710	<2	0.03	2256	24	12	2	<0.01	22	11	21
45137	<1	0.11	<10	5.3	<5	0.16	2	108	781	2	5.41	<0.01	25.58	722	<2	0.03	2251	14	14	2	<0.01	21	<10	20
45138	<1	0.10	<10	5.5	<5	0.04	2	111	1078	1	5.65	<0.01	26.06	754	<2	0.03	2335	10	15	1	<0.01	22	<10	23
45139	<1	0.10	<10	6.1	<5	0.65	2	112	1335	1	5.93	<0.01	24.02	1002	<2	0.02	2342	<10	21	18	<0.01	21	10	37
45140	<1	0.10	<10	5.5	<5	0.64	2	102	1233	3	5.57	<0.01	24.39	804	<2	0.03	2127	10	19	48	<0.01	19	<10	30
45141	<1	0.07	<10	5.0	<5	0.87	2	105	929	1	5.17	<0.01	24.06	828	<2	0.02	2200	<10	11	46	<0.01	16	<10	22
45142	<1	0.07	<10	5.3	<5	0.32	2	109	977	1	5.34	<0.01	24.52	788	<2	0.02	2331	16	13	6	<0.01	17	<10	24
45143	<1	0.07	<10	5.6	<5	0.32	2	114	1054	<1	5.64	<0.01	25.02	833	<2	0.02	2306	15	11	5	<0.01	17	<10	19
45144	<1	0.09	<10	6.6	<5	1.12	2	123	1351	2	6.76	<0.01	24.05	971	<2	0.02	2350	16	18	23	<0.01	19	<10	32
45145	<1	0.12	12	4.8	<5	0.55	2	102	953	<1	4.88	0.02	23.78	757	<2	0.04	2080	25	11	16	<0.01	17	<10	22
45146	<1	0.10	<10	5.9	<5	0.21	2	108	1173	<1	6.02	0.01	24.01	775	<2	0.04	2198	18	13	6	<0.01	18	10	20
45147	<1	0.08	<10	5.1	<5	0.03	2	105	867	<1	5.34	0.01	25.81	723	<2	0.04	2267	20	14	2	<0.01	17	<10	18
45148	<1	0.09	<10	5.5	<5	0.12	2	109	1448	1	5.55	0.01	24.41	727	<2	0.03	2169	21	16	2	<0.01	18	<10	22
45149	<1	0.10	<10	4.9	<5	0.36	2	110	1534	1	5.08	<0.01	24.63	786	<2	0.03	2317	39	14	3	<0.01	17	<10	24
45150	<1	0.08	<10	5.3	<5	0.11	2	103	1188	3	5.38	<0.01	24.15	725	<2	0.02	2130	21	14	2	<0.01	16	<10	20
45151	<1	0.07	<10	5.3	<5	0.12	2	104	1186	2	5.44	<0.01	24.72	838	<2	0.02	2091	18	12	2	<0.01	16	11	20
45152	<1	0.07	<10	4.5	<5	0.07	2	100	1208	<1	4.83	<0.01	24.49	824	<2	0.02	2083	16	11	1	<0.01	14	<10	20
45153	<1	0.07	<10	5.0	<5	0.19	2	108	1441	1	5.24	<0.01	24.93	889	<2	0.02	2262	23	12	3	<0.01	16	<10	19
45154	<1	0.22	<10	4.5	<5	0.20	2	101	7444	<1	4.61	<0.01	23.83	976	<2	0.01	2214	14	12	4	0.01	11	<10	37
45155	<1	0.13	<10	4.6	<5	0.10	2	98	2912	1	4.84	<0.01	23.77	854	<2	0.01	2055	18	18	1	<0.01	16	<10	30
45156	<1	0.08	<10	5.2	<5	0.20	2	106	1011	1	5.44	<0.01	25.40	830	<2	0.02	2216	20	16	8	<0.01	17	10	25
45157	<1	0.07	<10	5.4	<5	0.04	2	104	1469	<1	5.47	<0.01	24.63	774	<2	0.01	1958	20	13	1	<0.01	15	<10	24
45158	<1	0.06	<10	4.9	<5	0.14	2	111	1164	1	5.11	<0.01	25.18	743	<2	0.02	2348	18	12	3	<0.01	12	<10	18
45159	<1	0.05	<10	4.7	<5	0.08	2	106	979	<1	4.79	<0.01	25.23	701	<2	0.02	2204	20	10	3	<0.01	12	<10	16
45160	<1	0.07	<10	5.1	<5	0.13	2	105	1865	<1	5.18	0.01	24.51	719	<2	0.02	2282	13	15	3	<0.01	11	<10	18

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2906RR

Date : Nov-28-08

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
45161	<1	0.08	<10	5.0	<5	0.06	2	109	1692	<1	5.26	0.01	25.49	761	<2	0.02	2274	16	13	1	<0.01	12	12	21
45162	<1	0.06	10	4.8	<5	0.19	2	113	1670	<1	5.05	<0.01	24.49	847	<2	0.01	2328	17	21	3	<0.01	10	12	24
45163	<1	0.05	<10	4.7	<5	0.22	2	113	1038	2	4.90	<0.01	25.95	834	<2	0.01	2440	21	15	4	<0.01	12	<10	22
45164	<1	0.09	<10	5.3	<5	0.07	2	110	2421	<1	5.33	<0.01	24.66	892	<2	0.01	2261	16	17	3	<0.01	12	<10	30
45165	<1	0.09	<10	4.5	<5	0.04	2	105	908	<1	4.82	<0.01	24.75	700	<2	0.02	2258	18	13	1	<0.01	17	<10	21
45166	<1	0.08	<10	4.8	<5	0.09	2	104	1000	<1	5.04	<0.01	24.37	717	<2	0.02	2173	16	15	2	<0.01	16	<10	19
45167	<1	0.09	<10	5.3	<5	0.04	2	116	1062	<1	5.44	<0.01	25.62	752	<2	0.02	2386	<10	10	1	<0.01	19	<10	19
45168	<1	0.09	<10	5.2	<5	0.08	2	115	1213	<1	5.45	<0.01	25.39	732	<2	0.01	2389	18	11	2	<0.01	18	<10	20
45169	<1	0.08	<10	4.8	<5	0.10	2	106	1039	<1	5.00	<0.01	24.96	707	<2	0.01	2102	13	14	2	<0.01	15	<10	21
45170	<1	0.09	<10	5.1	<5	0.48	2	113	1720	<1	5.42	0.01	26.66	916	<2	0.01	2419	16	15	5	<0.01	15	<10	32
45171	<1	0.07	<10	4.9	<5	0.29	2	115	2117	<1	5.10	0.01	25.54	950	<2	0.01	2527	22	10	42	<0.01	11	<10	33
45172	<1	0.06	<10	5.4	<5	0.38	2	115	1255	<1	5.66	<0.01	25.87	916	<2	0.01	2296	23	20	12	<0.01	14	<10	31
45173	<1	0.08	<10	5.8	<5	0.73	2	104	1216	<1	5.95	<0.01	25.80	940	<2	0.02	1985	27	17	22	<0.01	16	<10	38
45174	<1	0.09	26	6.2	<5	0.17	2	117	1554	<1	6.15	<0.01	25.18	847	<2	0.01	2282	11	15	5	<0.01	18	<10	35
45175	<1	0.07	54	5.6	<5	0.32	2	124	945	<1	5.88	<0.01	27.10	871	<2	0.01	2540	19	12	58	<0.01	18	10	30
45176	<1	0.08	<10	5.3	<5	0.31	2	110	1079	<1	5.47	<0.01	25.39	808	<2	0.02	2265	18	11	40	<0.01	16	<10	32
45177	<1	0.08	14	4.7	<5	0.30	2	107	978	<1	5.00	<0.01	25.09	765	<2	0.01	2178	11	8	6	<0.01	16	<10	30
45178	<1	0.09	<10	5.2	<5	0.29	2	107	1152	<1	5.20	<0.01	24.50	761	<2	0.02	2178	16	11	6	<0.01	17	<10	30
45179	<1	0.07	11	5.1	<5	0.22	2	122	1158	<1	5.41	<0.01	24.42	681	<2	0.01	2495	16	11	6	<0.01	15	<10	30
45180	<1	0.06	<10	4.8	<5	0.62	2	119	884	<1	4.97	<0.01	24.59	712	<2	0.02	2455	20	10	40	<0.01	15	<10	29
45181	<1	0.12	<10	5.3	<5	0.49	2	103	1151	1	5.32	0.01	22.85	1008	<2	0.04	2130	13	12	95	<0.01	20	<10	38
45182	<1	0.12	<10	4.9	<5	1.30	3	96	904	9	4.89	0.01	21.46	1047	<2	0.05	1987	10	32	192	<0.01	19	<10	273
45183	<1	0.35	<10	7.5	<5	3.42	4	89	914	17	6.04	0.01	15.91	1084	<2	0.05	1796	37	78	325	0.01	27	<10	650
45194	<1	0.10	<10	5.5	<5	0.87	2	111	1150	<1	5.66	0.01	24.00	821	<2	0.03	2286	11	13	21	<0.01	18	<10	32
45195	<1	0.10	<10	5.5	<5	1.31	2	108	1050	<1	5.47	0.01	23.45	852	<2	0.02	2290	26	15	30	<0.01	20	<10	29
45196	<1	0.10	10	6.6	<5	1.66	3	113	1300	<1	6.71	0.01	24.16	918	<2	0.02	2302	22	10	27	<0.01	22	<10	33
45197	<1	3.71	11	6.8	<5	0.78	2	90	1059	65	6.73	0.01	19.64	923	<2	0.03	1817	376	7	15	0.19	131	<10	56
45198	<1	0.36	23	5.4	<5	1.85	2	96	1057	34	5.32	0.01	17.23	695	<2	0.04	2017	66	55	27	0.02	30	<10	65
45199	<1	0.20	22	5.1	<5	5.45	2	78	1029	14	5.07	0.01	15.44	972	<2	0.04	1530	39	16	99	0.01	23	<10	44
45200	<1	5.02	172	7.3	<5	2.76	2	75	764	30	7.19	0.80	13.29	1268	<2	0.38	1021	519	14	139	0.25	173	<10	108

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2906RR

Date : Nov-28-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
Duplicates:																								
45101	<1	0.11	<10	4.6	<5	1.73	2	100	2424	2	4.67	0.01	22.48	905	<2	0.01	2017	18	19	129	<0.01	10	<10	54
45110	<1	0.09	<10	5.8	<5	0.08	2	117	2325	<1	5.99	<0.01	25.05	950	<2	0.01	2299	21	16	8	<0.01	14	<10	31
45120	<1	0.16	<10	5.6	<5	0.18	2	113	1740	<1	5.56	<0.01	25.00	836	<2	0.02	2253	24	20	16	0.01	16	<10	34
45123	<1	0.19	28	5.5	<5	1.48	2	99	924	<1	5.48	0.04	23.54	987	<2	0.02	1876	42	25	67	0.01	20	<10	40
45132	<1	0.09	<10	5.7	<5	0.09	2	108	788	1	5.81	<0.01	24.28	704	<2	0.02	2078	12	13	4	<0.01	21	<10	20
45142	<1	0.07	<10	5.4	<5	0.31	2	110	1011	2	5.42	<0.01	24.62	798	<2	0.02	2327	12	12	6	<0.01	16	<10	21
45145	<1	0.10	10	4.7	<5	0.54	2	102	946	<1	4.92	0.01	23.82	765	<2	0.02	2070	25	14	16	<0.01	17	<10	23
45154	<1	0.23	<10	4.4	<5	0.19	2	102	7752	<1	4.61	<0.01	23.58	974	<2	0.01	2189	24	11	4	0.01	11	<10	37
45164	<1	0.09	<10	5.3	<5	0.07	2	110	2254	<1	5.40	<0.01	24.76	896	<2	0.02	2291	24	15	3	<0.01	12	<10	31
45167	<1	0.09	<10	5.1	<5	0.04	2	113	1050	<1	5.32	0.01	25.17	738	<2	0.02	2350	14	19	1	<0.01	18	<10	23
45176	<1	0.08	<10	5.4	<5	0.30	2	110	1073	<1	5.41	<0.01	25.34	804	<2	0.02	2267	17	12	39	<0.01	16	<10	33
45196	<1	0.10	<10	6.3	<5	1.57	2	106	1178	<1	6.29	0.01	22.97	865	<2	0.02	2171	16	13	26	<0.01	20	<10	31
45199	<1	0.21	20	5.2	<5	5.57	2	79	1064	14	5.17	0.01	15.71	995	<2	0.04	1553	39	11	102	0.01	23	<10	41
Standards:																								
Blank	<1	0.01	<10	<0.5	<5	<0.01	<1	1	2	1	0.01	<0.01	<0.01	<5	<2	0.01	1	<10	<2	<1	<0.01	<1	<10	<2
CH-4	2	7.59	482	6.2	<5	1.96	1	34	100	1986	5.60	1.81	1.51	469	<2	3.15	64	695	13	206	0.31	102	<10	229

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2995RR

Date : Dec-05-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
45201	<1	7.15	159	8.6	<5	1.66	1	70	1162	16	7.82	1.08	12.14	1316	<2	0.85	888	604	7	97	0.33	238	13	133
45202	2	3.99	16	7.8	<5	6.21	2	115	2086	289	7.24	0.09	13.20	1178	<2	0.11	2135	260	50	102	0.15	134	<10	112
45203	<1	0.45	<10	5.6	<5	3.44	2	93	1614	<1	5.21	0.01	19.67	1003	<2	0.03	1709	35	6	53	0.02	25	<10	46
45204	<1	0.20	<10	5.8	<5	2.72	2	108	1791	<1	5.35	<0.01	21.12	1003	<2	0.02	2123	<10	15	28	<0.01	18	<10	39
45205	<1	0.16	<10	5.4	<5	1.29	2	104	1473	<1	5.13	<0.01	21.87	860	<2	0.02	2167	<10	9	18	<0.01	18	<10	33
45206	<1	0.15	21	5.5	<5	1.35	2	102	1731	<1	5.04	0.01	22.23	1120	<2	0.03	2066	11	13	33	<0.01	17	<10	41
45207	<1	0.19	89	5.8	<5	0.60	2	110	2033	<1	5.37	0.01	22.96	1122	<2	0.03	1968	13	31	56	<0.01	16	<10	52
45208	<1	0.11	<10	6.3	<5	0.94	2	104	1495	<1	6.06	<0.01	22.81	831	<2	0.02	1958	16	19	62	<0.01	21	<10	42
45209	<1	0.08	12	5.5	<5	0.86	2	117	1576	<1	5.46	<0.01	24.73	1035	<2	0.01	2363	11	12	20	<0.01	14	<10	46
45210	<1	0.09	<10	5.8	<5	0.28	2	114	1771	<1	5.72	<0.01	24.49	902	<2	0.01	2284	<10	13	12	<0.01	14	13	43
45211	<1	0.09	53	5.4	<5	0.36	2	108	982	<1	5.35	0.01	24.33	854	<2	0.01	2203	11	23	25	<0.01	14	<10	36
45212	<1	0.06	30	5.4	<5	0.06	2	111	1092	<1	5.20	0.01	24.58	788	<2	0.01	2332	<10	20	6	<0.01	12	<10	28
45213	<1	0.06	10	5.7	<5	0.14	2	113	1365	<1	5.55	<0.01	24.43	809	<2	0.01	2196	11	11	13	<0.01	13	<10	22
45214	<1	0.06	<10	6.1	<5	0.58	2	115	1682	<1	5.98	<0.01	24.82	970	<2	0.01	2092	<10	13	39	<0.01	13	<10	20
45215	<1	0.06	<10	5.8	<5	0.09	2	121	1203	<1	5.67	<0.01	26.95	944	<2	0.01	2549	10	12	8	<0.01	13	<10	19
45216	<1	0.06	<10	5.7	<5	0.06	2	114	1528	<1	5.56	<0.01	24.98	755	<2	0.01	2287	12	14	6	<0.01	12	11	18
45217	<1	0.04	<10	4.3	<5	0.23	2	108	857	<1	4.35	<0.01	25.65	685	<2	0.01	2335	10	8	9	<0.01	10	12	16
45218	<1	0.05	<10	5.8	<5	0.14	2	109	1346	<1	5.68	<0.01	24.83	734	<2	0.01	2426	12	10	5	<0.01	12	<10	27
45219	<1	0.06	<10	6.0	<5	0.22	2	108	1967	<1	5.83	<0.01	24.47	896	<2	0.01	2187	11	10	7	<0.01	12	<10	18
45220	<1	0.06	<10	5.4	<5	<0.01	2	97	1372	<1	5.27	<0.01	23.73	674	<2	0.01	2178	13	9	1	<0.01	13	<10	17
45221	<1	0.06	<10	5.9	<5	0.02	2	101	1553	<1	5.81	<0.01	24.04	749	<2	0.01	2268	<10	10	4	<0.01	13	10	14
45222	<1	0.06	<10	4.7	<5	0.05	2	101	1502	<1	4.72	<0.01	24.87	647	<2	0.01	2354	<10	9	3	<0.01	10	<10	11
45223	1	0.14	32	5.1	<5	0.15	2	95	4614	<1	5.01	<0.01	23.74	853	<2	0.01	2151	12	19	5	<0.01	4	<10	29
45224	1	0.08	39	4.6	<5	0.31	2	90	1987	<1	4.62	<0.01	23.53	828	<2	0.01	2101	14	18	13	<0.01	10	<10	25
45225	<1	0.07	<10	5.4	<5	0.14	2	100	1364	<1	5.39	<0.01	24.42	777	<2	0.01	2134	17	7	12	<0.01	13	<10	25
45226	<1	0.05	13	5.3	<5	0.13	2	108	1145	<1	5.25	<0.01	24.99	800	<2	0.01	2288	14	14	13	<0.01	12	<10	24
45227	<1	0.08	<10	5.7	<5	0.05	2	109	1039	<1	5.57	<0.01	25.31	790	<2	0.01	2328	16	20	3	<0.01	15	<10	26
45228	1	0.12	15	5.8	<5	0.20	2	107	1225	<1	5.73	<0.01	24.21	824	<2	0.02	2230	14	13	2	<0.01	20	<10	30
45229	<1	0.12	12	6.3	<5	0.51	2	112	1485	<1	6.06	<0.01	25.24	997	<2	0.01	2289	11	14	3	<0.01	19	<10	33
45230	<1	0.07	<10	5.8	<5	0.27	2	104	1029	<1	5.57	<0.01	24.00	891	<2	0.01	2260	12	15	4	<0.01	15	<10	27

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2995RR

Date : Dec-05-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
45231	<1	0.09	<10	5.9	<5	0.28	2	109	1109	<1	5.90	<0.01	23.52	875	<2	0.01	2200	<10	12	2	<0.01	18	<10	25
45232	<1	0.09	<10	5.5	<5	0.30	2	99	1322	<1	5.36	<0.01	22.06	780	<2	0.02	2001	<10	12	2	<0.01	17	<10	28
45233	<1	0.60	14	5.9	<5	0.99	2	100	1003	<1	5.36	<0.01	20.90	853	<2	0.03	2061	35	15	3	0.02	30	<10	26
45234	<1	9.89	377	8.3	<5	3.13	1	47	57	109	7.77	0.14	13.59	2052	<2	0.33	45	934	<2	517	0.55	331	<10	74
45235	<1	0.20	<10	6.3	<5	0.11	2	106	1211	<1	6.11	<0.01	22.23	762	<2	0.03	2225	<10	16	4	<0.01	23	<10	27
45236	<1	0.20	10	6.0	<5	0.12	2	105	988	<1	5.63	<0.01	23.16	778	<2	0.02	2138	25	10	5	0.01	23	<10	25
45237	<1	0.19	12	5.9	<5	0.16	2	104	1049	<1	5.51	<0.01	22.81	774	<2	0.02	2123	21	11	1	0.01	22	<10	27
45238	<1	0.09	13	5.6	<5	0.60	2	105	1288	<1	5.53	<0.01	23.32	888	<2	0.02	2045	10	13	7	<0.01	17	<10	32
45239	<1	0.06	<10	5.3	<5	0.25	2	106	795	<1	5.09	<0.01	23.87	850	<2	0.01	2247	15	12	3	<0.01	14	<10	28
45240	<1	0.08	<10	5.9	<5	0.42	2	102	1230	<1	5.57	<0.01	22.35	786	<2	0.01	2091	10	12	8	<0.01	16	<10	30
45241	<1	0.09	<10	5.6	<5	0.72	2	100	1318	<1	5.40	<0.01	22.44	815	<2	0.01	1925	12	12	5	<0.01	17	<10	28
45242	<1	0.08	<10	5.6	<5	1.04	2	103	1058	<1	5.25	<0.01	22.47	846	<2	0.01	2158	11	13	15	<0.01	16	<10	29
45243	<1	0.09	<10	6.0	<5	0.09	2	107	1351	<1	5.80	<0.01	22.89	861	<2	0.01	2102	<10	12	4	<0.01	18	<10	32
45244	<1	0.08	<10	5.9	<5	0.29	2	101	1023	<1	5.28	<0.01	22.45	1116	<2	0.01	2112	10	18	8	<0.01	18	<10	58
45245	<1	0.09	<10	5.9	<5	0.19	2	75	1044	<1	5.38	0.01	19.94	992	<2	0.02	1721	10	33	8	<0.01	16	<10	143
45246	<1	0.07	<10	6.0	<5	0.15	2	109	1111	<1	5.83	<0.01	24.41	881	<2	0.01	2094	16	22	2	<0.01	17	<10	25
45247	<1	0.08	<10	6.0	<5	0.13	2	110	1136	<1	5.81	<0.01	24.32	832	<2	0.01	2222	19	13	1	<0.01	18	<10	22
45248	<1	0.08	<10	5.7	<5	0.23	2	111	1329	<1	5.58	<0.01	24.72	863	<2	0.01	2191	12	12	2	<0.01	16	<10	25
45249	<1	0.09	<10	5.5	<5	0.18	2	109	1433	<1	5.33	<0.01	24.90	927	<2	0.01	2125	17	13	4	<0.01	17	<10	25
45250	<1	0.12	<10	5.6	<5	0.11	2	112	1472	<1	5.59	<0.01	25.37	893	<2	0.01	2215	19	14	3	<0.01	20	<10	25
45251	<1	0.09	<10	5.8	<5	0.11	2	112	1477	<1	5.72	<0.01	25.32	887	<2	0.01	2302	22	12	3	<0.01	17	<10	24
45252	<1	0.11	<10	5.8	<5	0.19	2	112	1277	<1	5.71	<0.01	24.72	829	<2	0.01	2070	14	15	4	<0.01	20	<10	24
45253	<1	0.10	<10	5.9	<5	0.33	2	111	1573	<1	5.63	<0.01	24.20	972	<2	0.01	2084	14	15	8	<0.01	18	<10	28
45254	1	0.11	<10	5.8	<5	0.43	2	93	1784	<1	5.32	<0.01	22.51	1203	<2	0.02	1952	17	35	10	<0.01	16	<10	68
45255	<1	0.08	<10	6.0	<5	0.40	2	113	1883	<1	5.79	<0.01	23.92	1146	<2	0.02	2152	33	14	11	<0.01	15	<10	37
45256	<1	0.10	<10	6.0	<5	0.42	2	105	1928	<1	5.68	<0.01	22.37	1322	<2	0.02	1968	22	24	10	<0.01	16	<10	45
45257	<1	0.11	<10	5.7	<5	0.32	2	105	1633	<1	5.43	<0.01	24.36	1013	<2	0.01	2068	13	21	9	<0.01	17	<10	63
45258	<1	0.11	<10	5.8	<5	0.17	2	116	1726	<1	5.73	<0.01	25.92	918	<2	0.01	2214	18	14	4	<0.01	18	<10	26
45259	<1	0.11	<10	5.5	<5	0.23	2	106	1203	<1	5.53	<0.01	24.41	805	<2	0.02	2095	27	17	4	<0.01	17	<10	22
45260	<1	0.11	<10	5.2	<5	0.17	2	105	1191	<1	5.24	<0.01	24.23	810	<2	0.02	2030	<10	19	2	<0.01	17	<10	23

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2995RR

Date : Dec-05-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
45261	<1	0.11	<10	5.9	<5	0.27	2	107	1681	<1	5.70	<0.01	24.37	846	<2	0.01	2098	18	13	5	<0.01	17	<10	25
45262	<1	0.09	<10	5.8	<5	0.18	2	115	1576	<1	5.76	<0.01	25.45	907	<2	0.01	2275	20	16	4	<0.01	16	<10	25
45263	<1	0.09	<10	6.5	<5	0.26	2	118	1701	<1	6.25	<0.01	26.16	945	<2	0.01	2283	17	16	7	<0.01	17	<10	27
45264	<1	0.11	<10	5.3	<5	0.23	2	103	1642	<1	5.36	0.01	23.92	867	<2	0.02	2020	16	22	7	<0.01	16	<10	39
45265	<1	7.69	1662	8.5	<5	4.31	1	39	203	2	6.00	3.32	4.82	1616	<2	1.98	74	2473	5	945	0.59	170	<10	97
45266	<1	0.14	<10	5.7	<5	0.20	2	104	1040	<1	5.35	0.02	23.40	837	<2	0.03	2035	30	12	10	<0.01	20	<10	34
45267	<1	0.09	<10	5.5	<5	0.10	2	106	1160	<1	5.46	0.02	23.77	821	<2	0.02	2059	19	14	6	<0.01	16	11	31
45268	<1	0.11	<10	5.9	<5	0.34	2	109	1546	<1	5.73	0.01	24.00	864	<2	0.02	2057	12	12	7	<0.01	17	<10	33
45269	<1	0.10	<10	5.5	<5	0.19	2	107	1493	<1	5.34	<0.01	23.93	823	<2	0.02	2110	<10	15	5	<0.01	16	<10	33
45270	<1	0.13	<10	5.5	<5	0.07	2	107	1503	<1	5.37	<0.01	23.92	765	<2	0.02	2122	<10	10	2	<0.01	18	<10	27
45271	<1	0.10	<10	5.6	<5	0.18	2	110	2025	<1	5.49	<0.01	24.49	862	<2	0.01	2101	<10	15	4	<0.01	15	<10	29
45272	<1	0.09	<10	5.6	<5	0.12	2	112	2034	<1	5.45	<0.01	24.47	863	<2	0.02	2068	17	14	3	<0.01	14	<10	32
45273	<1	0.10	<10	5.4	<5	0.12	2	106	1108	<1	5.36	<0.01	24.49	794	<2	0.02	2102	15	11	3	<0.01	17	<10	25
45274	<1	0.10	<10	5.4	<5	0.07	2	104	1254	<1	5.40	<0.01	24.10	790	<2	0.02	2116	12	9	1	<0.01	16	<10	24
45275	<1	0.11	<10	5.8	<5	0.20	2	108	1229	<1	5.58	<0.01	24.66	824	<2	0.02	2126	14	13	3	<0.01	18	<10	25
45276	<1	0.09	<10	5.8	<5	1.62	2	108	1610	<1	5.56	0.01	21.75	825	<2	0.02	2346	24	8	24	<0.01	15	10	28
45277	<1	0.10	<10	6.3	<5	2.55	2	107	1722	<1	6.14	<0.01	22.58	1002	<2	0.02	2082	17	12	63	<0.01	18	<10	38
45278	<1	0.09	<10	5.3	<5	1.15	2	100	1308	<1	5.11	<0.01	22.98	854	<2	0.02	1957	12	10	113	<0.01	16	<10	38
45279	<1	0.10	<10	5.5	<5	0.99	2	101	1467	<1	5.51	<0.01	24.16	895	<2	0.02	1941	<10	23	42	<0.01	16	<10	38
45280	<1	0.05	<10	5.5	<5	1.38	2	99	1006	<1	5.48	<0.01	24.23	1150	<2	0.01	2076	<10	23	67	<0.01	12	<10	39
45281	<1	0.08	<10	5.4	<5	3.22	2	97	1131	<1	5.29	<0.01	20.89	1193	<2	0.02	1924	14	17	47	<0.01	14	<10	41
45282	<1	0.07	<10	5.5	<5	2.70	2	95	1232	<1	5.26	<0.01	21.05	1156	<2	0.01	1977	18	13	67	<0.01	13	<10	44
45291	<1	0.19	11	5.3	<5	6.19	2	91	1526	12	4.93	0.01	16.88	1031	<2	0.02	1748	25	12	37	0.01	16	<10	38
45292	<1	0.09	<10	5.7	<5	3.50	2	97	1375	7	5.30	<0.01	21.27	1372	<2	0.02	1926	23	8	42	<0.01	16	<10	31
45293	<1	0.07	<10	5.3	<5	2.11	2	91	1250	<1	4.98	0.01	20.31	1392	<2	0.02	1813	17	10	50	<0.01	14	<10	43
45294	<1	0.05	<10	5.8	<5	0.56	2	118	1067	<1	5.73	<0.01	24.64	997	<2	0.01	2209	11	10	20	<0.01	13	10	24
45295	<1	0.06	<10	5.4	<5	0.61	2	106	989	<1	5.34	<0.01	24.82	887	<2	0.01	2031	14	8	47	<0.01	14	<10	23
45296	<1	0.08	<10	5.5	<5	0.33	2	110	1380	<1	5.21	<0.01	23.89	972	<2	0.01	2136	11	11	16	<0.01	13	<10	30
45297	<1	0.10	<10	5.8	<5	0.27	2	107	1785	<1	5.65	<0.01	24.76	893	<2	0.02	2109	22	14	10	<0.01	16	<10	28
45298	<1	0.12	<10	5.7	<5	0.17	2	108	1440	<1	5.59	0.01	24.65	814	<2	0.02	2243	25	16	8	<0.01	19	<10	26

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V2995RR

Date : Dec-05-08

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
45299	<1	0.11	<10	6.1	<5	0.13	2	116	1734	<1	6.08	0.01	25.68	946	<2	0.03	2375	22	15	4	<0.01	18	<10	28
45300	<1	0.11	<10	5.5	<5	0.19	2	110	1524	<1	5.44	<0.01	25.14	893	<2	0.02	2194	20	10	2	<0.01	17	<10	28
Duplicates:																								
45201	<1	7.17	158	8.2	<5	1.67	1	71	1231	21	7.58	1.08	12.22	1326	<2	0.84	896	607	9	97	0.33	238	10	135
45210	<1	0.10	<10	5.8	<5	0.29	2	116	1845	<1	5.83	<0.01	25.00	917	<2	0.01	2359	16	9	12	<0.01	15	11	46
45220	<1	0.07	<10	5.8	<5	0.01	2	107	1519	<1	5.57	<0.01	25.10	709	<2	0.01	2346	10	13	1	<0.01	14	<10	17
45223	<1	0.13	43	5.0	<5	0.15	2	96	3847	<1	4.82	<0.01	23.47	831	<2	0.01	2133	21	24	6	<0.01	6	<10	29
45232	<1	0.10	<10	5.7	<5	0.32	2	103	1256	<1	5.53	<0.01	22.88	805	<2	0.02	2069	<10	17	3	<0.01	18	<10	26
45242	<1	0.09	<10	5.8	<5	1.08	2	108	1159	<1	5.53	<0.01	23.48	886	<2	0.01	2254	19	17	16	<0.01	16	<10	31
45245	<1	0.09	<10	6.0	<5	0.20	2	81	1342	<1	5.69	<0.01	21.29	1061	<2	0.02	1825	15	26	9	<0.01	16	<10	153
45254	<1	0.11	<10	5.3	<5	0.40	2	89	1681	<1	5.15	<0.01	21.70	1162	<2	0.02	1867	22	30	9	<0.01	16	<10	70
45264	<1	0.11	<10	5.3	<5	0.24	2	107	1587	<1	5.33	<0.01	23.65	862	<2	0.02	2056	15	26	7	<0.01	17	<10	42
45267	<1	0.10	<10	5.4	<5	0.10	2	104	1051	<1	5.29	0.02	23.96	827	<2	0.02	2059	14	9	6	<0.01	16	<10	30
45276	<1	0.10	<10	6.0	<5	1.69	2	110	1729	<1	5.76	0.01	22.64	853	<2	0.02	2439	25	8	25	<0.01	15	<10	27
45294	<1	0.05	<10	5.5	<5	0.55	2	113	869	<1	5.37	<0.01	24.68	996	<2	0.01	2150	13	9	19	<0.01	14	<10	25
45297	<1	0.09	<10	5.7	<5	0.27	2	109	1697	<1	5.66	<0.01	24.63	891	<2	0.02	2137	16	10	10	<0.01	17	<10	29
Standards:																								
Blank	<1	0.01	<10	<0.5	<5	<0.01	<1	2	3	<1	0.03	<0.01	<0.01	<5	<2	0.01	<1	<10	<2	<1	<0.01	<1	<10	<2
CH-4	2	7.76	471	6.2	<5	1.99	1	34	97	1975	5.25	1.88	1.48	473	<2	3.35	55	679	13	207	0.31	103	<10	232

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V3085RR

Date : Dec-01-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
45301	<1	0.12	11	5.6	<5	0.24	2	108	1475	<1	5.88	0.01	24.05	812	<2	0.02	2072	17	13	5	<0.01	19	<10	28
45302	<1	0.12	10	5.2	<5	0.22	2	101	1212	1	5.38	0.01	24.14	803	<2	0.03	2125	34	10	4	<0.01	18	<10	28
45303	<1	0.07	<10	5.3	<5	0.25	2	100	1103	<1	5.25	<0.01	22.21	790	<2	0.01	2014	16	8	2	<0.01	15	<10	24
45304	<1	0.11	<10	5.5	<5	0.32	2	103	1267	<1	5.59	<0.01	23.89	837	<2	0.04	2044	71	8	2	<0.01	19	<10	27
45305	<1	0.09	<10	5.1	<5	0.17	2	108	805	2	5.12	<0.01	24.66	797	<2	0.03	2344	49	7	3	<0.01	18	<10	26
45306	<1	0.08	<10	5.3	<5	0.03	2	105	1291	<1	5.36	<0.01	24.24	780	<2	0.05	2228	100	7	1	<0.01	15	11	28
45307	<1	0.03	<10	4.3	<5	0.08	2	110	470	<1	4.60	<0.01	26.07	788	<2	0.03	2378	66	8	2	<0.01	11	<10	20
45308	<1	0.05	<10	5.7	<5	0.30	2	105	894	<1	5.68	<0.01	24.47	884	<2	0.04	2149	82	15	7	<0.01	14	<10	25
45309	<1	0.07	<10	5.4	<5	0.06	2	106	1081	<1	5.55	<0.01	24.50	794	<2	0.06	2172	121	11	2	<0.01	15	<10	24
45310	<1	0.04	<10	5.7	<5	0.10	2	106	1210	<1	5.66	<0.01	24.42	798	<2	0.01	2171	15	12	2	<0.01	13	<10	18
45311	<1	0.03	<10	4.9	<5	0.04	2	107	606	<1	4.89	<0.01	25.67	753	<2	0.03	2270	61	8	2	<0.01	12	<10	16
45312	<1	0.05	<10	5.8	<5	0.01	2	111	1474	<1	5.90	<0.01	25.46	815	<2	0.02	2314	22	9	1	<0.01	13	<10	18
45313	<1	0.09	<10	5.1	<5	0.01	2	105	1174	<1	5.14	<0.01	24.64	729	<2	0.02	2202	15	8	1	<0.01	16	<10	17
45314	<1	0.05	<10	5.0	<5	<0.01	2	100	1165	<1	5.07	<0.01	25.14	680	<2	0.04	2280	82	9	<1	<0.01	13	<10	13
45315	<1	0.12	<10	5.3	<5	0.02	2	94	5489	<1	5.54	<0.01	23.86	838	<2	0.04	2258	83	11	1	<0.01	6	10	11
45316	<1	0.09	<10	5.5	<5	0.36	2	101	2830	<1	5.57	<0.01	24.70	888	<2	0.02	2109	24	21	9	<0.01	10	<10	25
45317	<1	0.07	<10	5.7	<5	0.07	2	107	2060	<1	5.83	<0.01	23.73	827	<2	0.06	2212	131	10	4	<0.01	14	<10	29
45318	<1	0.08	<10	5.2	<5	0.10	2	102	1334	<1	5.43	<0.01	23.63	827	<2	0.10	2070	240	7	4	<0.01	16	<10	28
45319	<1	0.11	<10	5.4	<5	0.20	2	101	1102	<1	5.31	<0.01	24.09	770	<2	0.11	2160	264	14	7	<0.01	19	<10	30
45320	<1	0.11	<10	4.7	<5	0.32	2	97	1119	<1	4.90	<0.01	23.63	776	<2	0.05	2013	110	11	23	<0.01	19	<10	29
45321	<1	0.09	<10	4.6	<5	2.82	2	84	957	14	4.28	<0.01	17.84	1297	<2	0.02	1671	41	29	710	<0.01	15	<10	96
45322	<1	0.14	<10	5.1	<5	1.95	2	97	1375	3	4.78	<0.01	18.38	1302	<2	0.04	1762	70	28	256	<0.01	18	<10	90
45323	<1	0.13	<10	5.0	<5	0.18	2	108	1443	<1	5.18	0.01	24.92	940	<2	0.03	2337	48	12	13	<0.01	20	<10	43
45324	<1	0.14	<10	5.7	<5	0.22	2	108	1519	<1	5.96	0.01	24.66	864	<2	0.02	2200	19	8	40	<0.01	22	<10	39
45325	<1	0.15	<10	5.8	<5	0.28	2	109	1486	<1	6.03	<0.01	25.11	912	<2	0.02	2248	31	10	4	<0.01	25	<10	39
45326	<1	0.11	<10	6.5	<5	0.54	3	113	1279	<1	6.68	<0.01	24.74	902	<2	0.03	2272	57	13	3	<0.01	24	11	36
45327	<1	0.08	<10	5.0	<5	0.45	2	107	1195	<1	5.26	<0.01	24.82	929	<2	0.02	2217	30	12	11	<0.01	17	<10	40
45328	<1	0.09	<10	6.1	<5	0.19	2	111	1618	<1	6.20	0.01	24.79	1004	<2	0.03	2215	19	11	9	<0.01	18	<10	38
45329	<1	0.05	<10	5.0	<5	0.14	2	110	1023	<1	5.32	<0.01	25.89	951	<2	0.01	2374	23	13	5	<0.01	15	<10	33
45330	<1	0.04	<10	6.1	<5	0.29	2	119	952	<1	6.27	<0.01	25.19	926	<2	0.01	2449	18	15	9	<0.01	18	<10	32

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V3085RR

Date : Dec-01-08

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
45331	<1	0.06	<10	5.2	<5	0.63	2	114	925	<1	5.41	0.01	24.44	989	<2	0.01	2470	30	9	13	<0.01	16	<10	34
45340	<1	0.09	<10	5.0	<5	0.21	2	106	1346	<1	5.26	<0.01	25.54	892	<2	0.02	2304	21	13	10	<0.01	16	<10	36
45341	<1	0.11	<10	5.1	<5	0.24	2	107	1498	<1	5.20	<0.01	25.11	911	<2	0.02	2293	24	12	2	<0.01	17	<10	40
45342	<1	0.11	<10	5.3	<5	0.02	2	106	1404	<1	5.63	<0.01	25.34	868	<2	0.02	2284	19	8	1	<0.01	20	<10	37
45343	<1	0.11	<10	5.8	<5	0.01	2	110	1585	3	5.82	<0.01	25.86	882	<2	0.01	2363	17	10	1	<0.01	18	<10	37
45344	<1	0.07	<10	5.1	<5	0.08	2	113	1211	<1	5.24	<0.01	26.10	897	<2	0.01	2438	19	18	<1	<0.01	15	<10	42
45345	<1	0.12	<10	5.4	<5	0.06	2	104	1306	<1	5.42	<0.01	24.45	808	<2	0.02	2205	23	10	<1	<0.01	20	<10	31
45346	<1	0.22	<10	5.6	<5	<0.01	2	106	1686	<1	5.88	0.05	24.44	889	<2	0.12	2248	21	8	<1	<0.01	22	<10	35
45347	<1	0.11	<10	5.4	<5	<0.01	2	109	1226	1	5.68	<0.01	26.14	855	<2	0.01	2396	16	6	<1	<0.01	19	<10	31
45348	<1	0.11	<10	5.3	<5	<0.01	2	107	1568	<1	5.51	<0.01	24.52	843	<2	0.02	2200	18	9	<1	<0.01	17	<10	29
45349	<1	0.11	<10	5.4	<5	0.01	2	105	1150	<1	5.50	<0.01	25.06	846	<2	0.02	2225	27	10	<1	<0.01	19	<10	28
45350	<1	0.11	<10	5.3	<5	0.08	2	109	1309	<1	5.47	<0.01	25.60	909	<2	0.02	2396	18	7	1	<0.01	18	<10	29
45351	<1	0.11	<10	5.0	<5	0.08	2	107	1191	<1	5.16	<0.01	25.76	915	<2	0.02	2323	22	13	1	<0.01	18	<10	29
45352	<1	0.13	<10	5.3	<5	0.09	2	105	1280	<1	5.34	<0.01	24.54	894	<2	0.02	2213	22	11	<1	<0.01	20	<10	29
45354	<1	0.10	<10	6.0	<5	0.36	2	113	2421	<1	6.02	<0.01	24.08	1019	<2	0.01	2302	19	14	21	<0.01	14	<10	39
45355	<1	0.11	<10	5.4	<5	0.40	2	110	1997	<1	5.70	0.01	24.67	902	<2	0.02	2235	28	15	31	<0.01	14	<10	32
45356	<1	0.10	<10	5.1	<5	0.24	2	106	1507	<1	5.23	<0.01	24.54	854	<2	0.02	2160	33	8	13	<0.01	15	13	34
45357	<1	0.07	<10	5.9	<5	0.05	2	117	1598	<1	6.15	<0.01	26.43	922	<2	0.02	2488	17	8	3	<0.01	14	10	29
45358	<1	0.07	<10	5.3	<5	0.25	2	103	1690	<1	5.44	<0.01	23.71	1376	<2	0.01	2147	18	12	12	<0.01	14	<10	43
45359	<1	0.06	<10	5.8	<5	0.09	2	112	1125	<1	5.98	0.01	24.98	933	<2	0.01	2365	16	16	5	<0.01	15	10	34
45360	<1	0.08	<10	5.0	<5	0.22	2	110	1319	<1	5.14	0.01	25.55	1003	<2	0.02	2147	17	10	9	<0.01	14	10	34
45361	<1	0.07	<10	5.4	<5	0.14	2	110	1115	<1	5.51	<0.01	25.38	915	<2	0.01	2287	15	11	6	<0.01	15	<10	28
45362	<1	0.07	<10	5.3	<5	0.18	2	107	1489	<1	5.45	<0.01	24.09	905	<2	0.02	2188	15	11	10	<0.01	14	<10	41
45363	<1	0.06	<10	5.8	<5	0.16	2	119	1893	<1	5.82	<0.01	25.96	983	<2	0.01	2368	16	8	7	<0.01	12	13	32
45364	<1	0.08	<10	5.0	<5	0.20	2	112	1550	<1	5.30	<0.01	25.69	965	<2	0.02	2337	<10	13	8	<0.01	13	<10	30
45365	<1	0.08	<10	5.7	<5	0.12	2	114	1679	<1	5.86	<0.01	25.71	910	<2	0.01	2295	16	5	5	<0.01	14	<10	28
45366	<1	0.09	<10	5.7	<5	0.26	2	120	1476	<1	5.94	<0.01	26.87	929	<2	0.02	2355	18	8	6	<0.01	16	<10	28
45367	<1	0.07	<10	5.3	<5	0.35	2	106	1350	<1	5.38	<0.01	24.52	842	<2	0.02	2159	<10	9	5	<0.01	15	<10	25
45368	<1	0.07	<10	5.4	<5	0.17	2	110	1091	<1	5.53	<0.01	25.41	872	<2	0.02	2295	17	11	2	<0.01	15	<10	25
45369	<1	0.06	<10	4.8	<5	0.26	2	116	1444	<1	5.16	<0.01	25.70	906	<2	0.01	2325	12	8	4	<0.01	12	<10	24

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V3085RR

Date : Dec-01-08

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
45370	<1	0.05	<10	5.0	<5	0.14	2	115	1117	<1	5.27	<0.01	25.27	906	<2	0.01	2352	11	4	3	<0.01	12	<10	21
45371	<1	0.07	<10	5.9	<5	0.43	2	112	1139	<1	5.88	<0.01	25.40	890	<2	0.02	2308	17	7	6	<0.01	15	<10	22
45372	<1	0.07	<10	5.4	<5	0.74	2	110	1704	<1	5.51	<0.01	24.75	926	<2	0.02	2088	15	9	9	<0.01	13	10	24
45373	<1	0.07	<10	5.3	<5	0.18	2	108	924	<1	5.54	<0.01	25.22	830	<2	0.02	2169	<10	7	4	<0.01	14	11	23
45374	<1	0.08	<10	6.0	<5	0.48	2	114	1965	<1	5.98	<0.01	25.35	918	<2	0.02	2153	10	11	6	<0.01	15	<10	27
45375	<1	0.06	<10	5.3	<5	0.20	2	114	1342	<1	5.55	<0.01	26.38	937	<2	0.01	2200	10	12	6	<0.01	12	<10	23
45376	<1	0.06	<10	5.5	<5	0.12	2	114	1171	<1	5.47	<0.01	25.11	880	<2	0.02	2008	11	7	5	<0.01	12	10	24
45377	<1	0.07	<10	5.5	<5	0.33	3	103	1489	<1	5.38	<0.01	22.93	1119	<2	0.03	1770	13	169	12	<0.01	13	<10	298
45378	<1	0.08	<10	6.8	<5	0.23	3	107	1944	<1	6.69	<0.01	23.91	905	<2	0.01	1969	19	20	12	<0.01	13	12	21
45379	<1	0.07	<10	5.4	<5	0.10	2	105	1875	<1	5.14	<0.01	24.54	796	<2	0.02	2065	25	13	5	<0.01	11	<10	22
45380	<1	0.06	<10	4.9	<5	0.14	2	99	1356	<1	4.76	<0.01	25.41	799	<2	0.02	2129	17	26	5	<0.01	10	<10	12
45381	<1	0.32	<10	4.0	<5	0.22	1	85	>10000	<1	4.04	<0.01	21.65	1024	<2	0.01	1886	14	13	8	0.01	<1	12	<2
45382	<1	0.26	<10	4.4	<5	0.08	2	81	>10000	<1	4.48	<0.01	22.48	897	<2	0.01	2088	12	12	3	0.01	<1	11	12
45383	<1	0.26	<10	4.5	<5	0.08	2	88	>10000	<1	4.46	<0.01	21.19	1061	<2	0.01	1888	14	10	3	0.01	<1	10	14
45384	<1	0.26	<10	2.8	<5	0.07	1	65	7574	<1	2.87	<0.01	19.57	828	<2	0.01	1704	12	7	3	0.01	<1	<10	4
45385	<1	0.28	<10	3.3	<5	0.07	1	62	7582	<1	3.32	0.01	19.21	806	<2	0.02	1575	10	12	5	0.01	<1	<10	9
45386	<1	0.25	<10	5.0	<5	0.35	2	92	9724	<1	4.76	0.01	22.49	1767	<2	0.02	1570	24	50	27	0.01	<1	<10	92
45387	<1	0.12	<10	5.7	<5	0.09	2	92	4524	<1	5.44	0.01	24.00	919	<2	0.02	2048	15	30	4	0.01	6	12	65
45388	<1	0.09	<10	5.5	<5	0.19	2	110	2590	3	5.58	0.01	26.15	839	<2	0.01	2094	17	13	6	<0.01	10	10	28
45389	<1	0.06	<10	5.2	<5	0.08	2	110	1078	<1	5.21	0.01	25.62	759	<2	0.01	2121	14	9	3	<0.01	12	<10	17
45390	<1	0.11	<10	5.4	<5	0.12	2	113	3260	3	5.48	0.01	25.24	940	<2	0.01	2037	14	12	4	<0.01	10	<10	36
45391	<1	0.10	<10	6.0	<5	0.11	2	121	3161	<1	6.04	0.01	25.86	960	<2	0.02	2125	18	15	4	<0.01	11	<10	40
45392	<1	0.08	<10	7.2	<5	0.11	3	112	2023	<1	7.18	0.01	24.68	791	<2	0.03	1874	20	15	4	<0.01	17	13	33
45393	<1	0.15	<10	6.0	<5	0.13	2	108	5519	1	6.02	0.01	24.40	844	<2	0.03	1548	20	11	5	<0.01	10	11	81
45394	<1	0.08	<10	5.8	<5	0.11	2	101	1808	1	5.85	0.01	24.71	727	<2	0.03	1382	17	18	6	<0.01	18	10	39
45395	<1	0.17	20	5.8	<5	0.59	2	108	1504	<1	5.59	0.03	23.72	877	<2	0.05	1756	44	9	52	0.01	18	10	41
45397	<1	0.10	<10	5.4	<5	0.20	2	104	1217	1	5.34	0.01	23.33	976	<2	0.02	1940	16	13	32	<0.01	15	<10	128
45398	12	0.09	<10	5.8	63	1.37	>100	90	1134	318	5.52	0.01	18.11	1118	<2	0.03	1546	14	1207	136	<0.01	15	<10	>10000
45399	<1	0.10	<10	6.2	<5	0.45	3	112	2397	<1	5.87	0.01	23.93	1166	<2	0.02	1967	15	20	55	<0.01	13	<10	273
45400	<1	7.41	1901	8.1	<5	3.91	6	44	336	17	5.91	3.48	5.95	2314	<2	1.74	193	2440	781	796	0.57	173	<10	1075

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V3085RR

Date : Dec-01-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
Duplicates:																								
45301	<1	0.04	<10	5.7	<5	0.10	2	106	1259	<1	5.70	<0.01	24.16	793	<2	0.02	2147	30	9	2	<0.01	13	<10	18
45310	<1	0.11	11	5.9	<5	0.24	2	107	1306	<1	5.90	0.01	24.09	815	<2	0.02	2055	22	15	5	<0.01	20	<10	29
45320	<1	0.12	<10	4.8	<5	0.32	2	96	1248	<1	4.87	<0.01	23.45	774	<2	0.05	2012	94	10	23	<0.01	19	10	31
45323	<1	0.13	<10	4.9	<5	0.18	2	109	1333	<1	5.16	0.01	24.99	939	<2	0.02	2327	22	10	14	<0.01	20	<10	40
45340	<1	0.10	<10	5.2	<5	0.08	2	109	1237	<1	5.62	<0.01	26.07	923	<2	0.01	2424	20	12	<1	<0.01	18	<10	28
45350	<1	0.09	<10	4.9	<5	0.20	2	105	1375	<1	5.14	<0.01	24.91	875	<2	0.02	2269	26	7	9	<0.01	16	<10	36
45354	<1	0.09	<10	5.8	<5	0.36	2	111	2110	<1	5.90	<0.01	24.11	1010	<2	0.01	2281	19	12	21	<0.01	15	<10	35
45363	1	0.06	<10	5.7	<5	0.16	2	121	1787	1	5.92	0.01	26.44	998	<2	0.02	2468	17	10	8	<0.01	12	<10	32
45373	<1	0.07	<10	5.3	<5	0.18	2	111	977	<1	5.62	<0.01	25.74	846	<2	0.02	2230	<10	10	4	<0.01	14	12	25
45376	<1	0.06	<10	5.9	<5	0.13	2	122	1407	<1	5.94	0.01	26.83	941	<2	0.01	2194	17	19	6	<0.01	12	<10	102
45385	<1	0.29	<10	3.2	<5	0.07	1	62	9023	<1	3.34	0.01	18.83	817	<2	0.02	1546	14	14	4	0.01	<1	<10	29
45395	<1	0.17	19	5.8	<5	0.59	2	104	1583	<1	5.68	0.03	23.79	881	<2	0.05	1716	47	11	52	0.01	17	<10	49
45399	<1	0.11	<10	6.0	<5	0.46	3	117	2456	<1	5.96	0.02	24.04	1181	<2	0.02	2016	28	21	56	0.01	14	<10	315
Standards:																								
Blank	<1	0.01	<10	<0.5	<5	<0.01	<1	1	<1	2	0.01	<0.01	0.01	<5	<2	0.01	2	<10	<2	<1	<0.01	<1	<10	<2
CH-4	2	7.91	468	6.1	<5	2.01	1	31	134	2061	5.43	1.93	1.43	464	<2	3.49	54	655	10	210	0.32	99	<10	232

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V3175RR

Date : Dec-02-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridg South

Sample type:

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
45401	<1	0.12	<10	4.9	<5	0.15	2	116	1436	3	5.18	0.01	25.54	1110	<2	0.02	2242	21	21	7	<0.01	15	<10	64
45402	<1	0.09	<10	5.8	<5	0.20	2	112	907	1	5.84	<0.01	25.81	950	<2	0.02	2308	19	17	6	<0.01	17	<10	36
45403	<1	0.11	<10	5.7	<5	0.15	2	110	945	1	5.79	<0.01	25.78	864	<2	0.02	2333	24	11	4	<0.01	19	<10	40
45404	2	0.11	<10	5.6	<5	0.16	38	109	916	177	5.69	<0.01	25.06	880	<2	0.03	2243	34	39	5	<0.01	18	<10	7139
45405	<1	0.09	<10	6.3	<5	0.09	3	109	999	18	6.64	<0.01	24.11	901	<2	0.02	2321	29	14	3	<0.01	19	<10	129
45406	<1	0.10	<10	5.2	<5	0.15	2	110	855	<1	5.35	<0.01	25.07	813	<2	0.02	2301	22	13	5	<0.01	18	<10	46
45407	<1	0.12	<10	5.3	<5	0.24	2	107	771	<1	5.38	<0.01	24.59	775	<2	0.02	2247	19	10	4	<0.01	22	<10	29
45408	<1	0.12	<10	5.3	<5	0.22	2	108	920	<1	5.40	<0.01	25.01	839	<2	0.02	2306	11	15	4	<0.01	20	<10	30
45409	<1	0.13	<10	5.3	<5	0.16	2	106	865	<1	5.39	<0.01	24.53	797	<2	0.02	2275	15	15	4	<0.01	20	<10	26
45410	<1	0.11	<10	6.0	<5	0.36	3	106	1447	7	6.02	<0.01	23.26	994	<2	0.02	2321	14	18	10	<0.01	19	<10	77
45411	<1	0.12	<10	5.7	<5	0.37	2	109	1252	<1	5.78	<0.01	26.11	1022	<2	0.02	2153	22	14	13	<0.01	21	11	46
45412	<1	0.12	<10	5.7	<5	0.17	2	109	1124	<1	5.81	<0.01	25.25	864	<2	0.02	2283	15	15	3	<0.01	21	<10	30
45413	<1	0.13	<10	6.4	<5	0.08	3	112	1570	<1	6.58	<0.01	24.92	794	<2	0.02	2387	19	13	2	<0.01	21	10	26
45414	<1	0.11	<10	5.0	<5	0.22	2	115	1493	<1	5.44	<0.01	26.29	846	<2	0.02	2409	16	13	8	<0.01	18	<10	31
45415	<1	0.10	<10	5.2	<5	0.21	2	109	1703	<1	5.42	<0.01	26.33	901	<2	0.01	2329	21	11	8	<0.01	16	10	29
45416	<1	0.07	<10	5.9	<5	0.21	2	110	1048	<1	5.98	<0.01	26.47	843	<2	0.01	2481	24	15	5	<0.01	17	<10	21
45417	<1	0.06	<10	5.1	<5	0.42	2	107	1039	<1	5.49	<0.01	26.11	844	<2	0.02	2467	22	17	8	<0.01	15	<10	25
45418	<1	0.08	<10	5.9	<5	0.37	2	110	1254	<1	6.17	<0.01	25.68	896	<2	0.04	2555	91	17	7	<0.01	17	<10	33
45419	<1	0.12	<10	6.8	<5	0.06	3	109	1847	<1	6.90	<0.01	24.84	809	<2	0.02	2426	17	12	2	<0.01	21	<10	28
45420	<1	0.09	<10	5.8	<5	0.10	2	109	978	<1	6.17	<0.01	26.83	830	<2	0.02	2439	15	13	2	<0.01	19	<10	24
45421	<1	0.07	<10	5.6	<5	0.11	2	105	879	2	5.74	<0.01	26.12	780	<2	0.01	2482	13	14	4	<0.01	17	10	20
45422	<1	0.09	<10	5.4	<5	0.10	2	102	835	1	5.43	<0.01	26.36	770	<2	0.02	2429	16	10	2	<0.01	16	<10	21
45423	<1	0.09	<10	5.5	<5	0.11	2	97	1110	<1	5.61	<0.01	24.88	740	<2	0.02	2275	13	14	3	<0.01	16	<10	18
45424	<1	0.11	<10	5.3	<5	0.11	2	97	1033	<1	5.45	0.01	24.82	712	<2	0.02	2311	11	11	1	<0.01	18	<10	19
45425	<1	0.12	<10	5.5	<5	0.12	2	98	1158	<1	5.60	0.06	25.55	733	<2	0.02	2314	18	11	2	<0.01	18	<10	20
45426	<1	0.12	<10	5.9	<5	0.09	2	103	1123	<1	5.96	<0.01	26.25	754	<2	0.02	2446	21	11	3	<0.01	19	<10	23
45427	<1	0.13	<10	6.4	<5	0.08	3	106	1505	<1	6.53	0.01	27.12	805	<2	0.03	2414	22	11	3	<0.01	20	<10	21
45428	<1	0.11	<10	6.0	<5	0.04	3	102	1270	<1	6.30	<0.01	26.90	786	<2	0.02	2434	18	12	2	<0.01	18	<10	20
45429	<1	0.11	<10	5.6	<5	0.07	2	100	1828	<1	5.71	0.01	26.99	802	<2	0.02	2415	18	12	2	<0.01	15	<10	24
45430	<1	0.09	<10	6.0	<5	0.07	2	101	1336	<1	6.18	<0.01	27.93	789	<2	0.02	2624	20	15	2	<0.01	17	<10	20

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V3175RR

Date : Dec-02-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridg South

Sample type:

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
45431	<1	0.09	<10	6.1	<5	0.26	2	100	1331	<1	6.09	<0.01	26.70	823	<2	0.01	2389	21	13	3	<0.01	16	<10	21
45432	<1	0.09	<10	6.1	<5	0.08	3	101	1417	<1	6.38	<0.01	25.82	788	<2	0.02	2415	17	12	1	<0.01	18	<10	20
45433	<1	0.08	<10	5.8	<5	0.20	2	99	1066	<1	5.73	<0.01	25.48	772	<2	0.02	2347	16	11	2	<0.01	16	<10	19
45434	<1	0.13	<10	5.5	<5	0.09	2	92	1263	<1	5.60	<0.01	24.71	694	<2	0.03	2229	16	12	1	<0.01	19	<10	22
45435	<1	1.11	192	8.0	<5	0.26	3	113	1098	1	7.21	0.60	22.37	1227	<2	0.43	2186	198	37	108	0.05	23	<10	71
45436	<1	0.05	<10	5.7	<5	0.07	2	116	992	<1	5.79	<0.01	25.18	1100	<2	0.01	2365	19	13	4	<0.01	13	<10	33
45437	<1	0.05	<10	6.1	<5	0.03	2	118	1233	<1	6.12	<0.01	25.62	956	<2	0.01	2440	16	11	2	<0.01	12	12	31
45438	<1	0.03	<10	5.2	<5	0.06	2	112	709	<1	5.24	<0.01	24.76	770	<2	0.01	2322	17	11	3	<0.01	11	<10	22
45439	<1	0.03	<10	5.2	<5	<0.01	2	109	645	<1	5.23	<0.01	24.84	769	<2	0.01	2314	23	11	1	<0.01	11	<10	21
45440	<1	0.03	<10	5.8	<5	<0.01	2	110	609	<1	5.64	0.06	24.60	746	<2	0.01	2270	15	11	2	<0.01	14	<10	22
45441	<1	0.05	<10	5.8	<5	0.08	2	114	951	<1	5.92	0.01	24.34	775	<2	0.01	2320	18	14	6	<0.01	13	<10	30
45442	<1	0.12	<10	5.8	<5	0.28	2	111	1354	<1	5.89	<0.01	24.23	880	<2	0.02	2198	18	11	16	<0.01	19	<10	33
45443	<1	0.14	<10	5.1	<5	0.17	2	102	1098	2	5.16	<0.01	23.65	802	<2	0.02	2141	12	8	7	<0.01	21	<10	26
45444	<1	0.13	<10	5.5	<5	0.11	2	107	1166	<1	5.57	<0.01	24.53	835	<2	0.02	2233	18	11	4	<0.01	21	<10	30
45445	<1	0.10	<10	5.7	<5	0.27	2	106	1245	<1	5.92	<0.01	22.95	846	<2	0.02	2195	20	15	11	<0.01	19	<10	35
45446	<1	0.13	<10	5.0	<5	0.17	2	103	1361	<1	5.09	<0.01	24.45	816	<2	0.02	2176	17	15	12	<0.01	17	<10	42
45447	<1	0.06	<10	4.9	<5	0.93	2	107	1137	<1	4.97	<0.01	23.28	1236	<2	0.01	2250	23	18	46	<0.01	12	<10	42
45448	<1	0.09	<10	5.2	<5	0.08	2	109	1328	<1	5.28	<0.01	24.14	1175	<2	0.01	2247	18	14	6	<0.01	14	<10	34
45449	<1	0.07	<10	5.5	<5	0.23	2	121	1510	1	5.61	<0.01	26.59	1460	<2	0.01	2551	28	50	9	<0.01	12	<10	86
45450	<1	0.07	<10	5.5	<5	0.41	2	114	1298	<1	5.52	<0.01	24.49	1017	<2	0.02	2353	42	18	23	<0.01	13	<10	34
45451	<1	0.07	<10	5.4	<5	0.77	2	114	1362	8	5.69	0.01	25.10	1147	<2	0.02	2286	40	18	67	<0.01	15	11	41
45452	<1	0.08	<10	5.3	<5	0.97	2	105	894	5	5.40	<0.01	23.82	1381	<2	0.02	2185	29	13	40	<0.01	16	<10	48
45453	<1	0.10	<10	5.3	<5	1.17	2	111	678	4	5.22	<0.01	22.37	748	<2	0.02	2092	24	12	31	<0.01	19	<10	29
45454	<1	0.07	<10	5.3	<5	0.21	2	111	915	1	5.60	0.01	24.64	603	<2	0.03	2490	40	16	18	<0.01	17	<10	25
45455	<1	2.92	<10	6.2	<5	0.34	2	89	960	6	6.27	0.04	21.07	1087	<2	0.05	1427	277	20	24	0.14	120	<10	76
45456	<1	4.28	13	6.0	<5	0.93	1	77	542	10	5.97	0.13	19.06	896	<2	0.02	1189	386	6	45	0.19	155	<10	57
45457	<1	0.11	<10	5.5	<5	0.26	2	108	1065	6	5.54	0.01	23.88	770	<2	0.03	2381	26	15	20	<0.01	20	<10	30
45458	<1	0.09	<10	4.7	<5	1.01	2	89	1061	27	4.82	0.01	23.71	868	<2	0.03	2184	26	16	31	<0.01	18	<10	28
45459	<1	6.82	168	7.1	<5	1.69	1	52	424	53	7.01	0.69	11.71	1184	<2	1.26	532	659	<2	415	0.34	247	<10	53
45460	<1	9.82	236	8.6	<5	3.94	1	41	47	59	8.04	0.89	4.93	1254	<2	2.99	36	878	<2	1150	0.51	377	<10	55

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V3175RR

Date : Dec-02-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridg South

Sample type:

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
45461	<1	9.41	376	8.2	<5	2.88	1	44	39	6	7.69	1.11	4.42	1282	<2	3.26	29	845	<2	774	0.50	350	<10	53
45462	<1	9.75	494	8.2	<5	2.22	<1	46	40	33	7.74	1.23	4.41	1286	<2	3.65	30	891	<2	607	0.51	362	<10	53
45463	<1	9.76	434	8.3	<5	2.50	<1	46	43	35	7.79	1.36	4.20	1283	<2	3.63	27	852	<2	537	0.51	375	<10	54
45464	<1	9.64	489	8.7	<5	2.01	1	49	35	33	7.89	1.40	4.38	2176	<2	3.41	26	856	249	508	0.52	365	<10	119
45465	<1	9.55	478	8.3	<5	1.47	1	47	34	54	7.79	1.64	4.42	1953	<2	3.54	29	841	32	335	0.51	350	<10	93
45466	<1	10.27	634	7.9	<5	1.71	<1	46	27	39	7.46	2.32	4.20	1830	<2	3.12	25	760	46	399	0.49	356	<10	170
45467	<1	9.92	784	7.9	<5	1.68	<1	43	25	77	7.41	2.66	3.77	2188	<2	2.78	26	694	45	322	0.48	347	<10	159
45468	<1	9.80	476	8.3	<5	1.45	<1	45	25	59	7.54	2.05	4.27	2214	<2	3.11	31	770	101	361	0.50	360	10	138
45469	<1	9.59	403	7.4	<5	1.35	<1	41	74	56	6.77	1.61	4.26	2342	<2	3.42	55	842	44	338	0.47	306	<10	122
45470	<1	0.44	10	4.6	<5	2.81	2	77	1840	12	4.44	0.01	19.14	1105	<2	0.03	1858	39	12	29	0.02	20	<10	44
45471	<1	0.10	<10	5.0	<5	1.31	2	88	1310	7	4.88	0.01	21.03	965	<2	0.02	2078	10	10	21	<0.01	15	10	33
45472	<1	0.10	<10	5.3	<5	0.70	2	96	1159	5	5.41	<0.01	21.78	788	<2	0.02	2139	10	5	8	<0.01	19	10	41
45473	<1	0.09	<10	5.2	<5	1.32	2	94	1211	7	5.15	<0.01	21.54	927	<2	0.01	2028	<10	7	10	<0.01	17	10	50
45474	1	0.08	<10	5.0	<5	1.32	2	96	971	14	5.28	<0.01	22.17	1212	<2	0.02	2164	16	8	15	<0.01	18	10	49
45475	<1	0.08	<10	5.4	<5	1.06	2	92	953	45	5.44	0.01	21.99	1137	<2	0.02	2102	16	10	8	<0.01	18	<10	44
45476	<1	0.06	<10	5.3	<5	1.28	2	97	954	31	5.29	<0.01	21.88	903	<2	0.02	2260	12	7	11	<0.01	18	<10	36
45477	<1	0.09	<10	5.1	<5	1.16	2	98	1329	11	5.22	<0.01	22.98	872	<2	0.02	2170	16	7	11	<0.01	16	<10	51
45478	<1	0.12	16	5.2	<5	0.91	2	93	1083	8	5.19	0.02	22.07	769	<2	0.04	2109	20	13	32	<0.01	19	<10	35
45479	<1	4.23	<10	6.4	<5	2.14	1	84	657	174	6.30	0.04	16.84	1082	<2	0.05	1298	380	3	58	0.21	159	<10	48
45480	<1	0.68	<10	5.7	<5	0.31	2	106	517	50	5.53	0.02	21.36	693	<2	0.02	2115	94	7	12	0.03	40	13	28
45481	<1	0.09	<10	5.1	<5	0.07	2	103	1052	8	5.14	<0.01	21.93	608	<2	0.02	2085	11	8	4	<0.01	17	11	20
45482	<1	0.07	<10	5.2	<5	0.45	2	116	959	6	5.49	0.01	24.21	669	<2	0.02	2367	16	4	3	<0.01	18	10	24
45483	<1	0.05	<10	5.4	<5	0.70	2	109	896	6	5.49	<0.01	23.85	749	<2	0.02	2199	15	11	6	<0.01	15	12	22
45484	<1	0.07	<10	5.4	<5	0.27	2	108	914	<1	5.55	<0.01	23.74	775	<2	0.02	2221	16	9	4	<0.01	17	10	20
45485	<1	1.36	<10	5.2	<5	0.47	2	84	1105	5	5.20	0.03	21.13	903	<2	0.02	1819	158	5	8	0.06	47	10	37
45486	<1	0.15	<10	5.0	<5	0.54	2	103	1013	5	5.06	<0.01	21.98	724	<2	0.01	2192	14	10	6	0.01	17	13	27
45487	<1	0.07	<10	5.0	<5	0.62	2	98	925	<1	5.08	<0.01	22.32	737	<2	0.01	2088	<10	9	4	<0.01	15	<10	22
45488	<1	0.07	<10	5.2	<5	0.53	2	97	1210	<1	5.28	<0.01	22.31	800	<2	0.01	2134	<10	6	4	<0.01	14	10	24
45489	<1	0.08	32	5.5	<5	0.20	2	113	1636	<1	5.38	0.01	24.28	955	<2	0.02	2399	27	17	4	<0.01	13	<10	39
45490	<1	0.11	17	5.6	<5	0.18	2	109	1169	<1	5.52	0.01	24.58	969	<2	0.02	2205	17	22	5	<0.01	15	<10	37

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V3175RR

Date : Dec-02-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridg South

Sample type:

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
45491	<1	0.09	<10	5.7	<5	0.41	2	117	1601	<1	5.55	0.01	25.44	1028	<2	0.01	2548	24	23	35	<0.01	14	<10	44
45492	<1	0.09	<10	5.4	<5	0.52	2	103	2834	<1	5.20	0.01	23.19	1054	<2	0.01	2273	18	15	6	<0.01	11	<10	57
45493	<1	0.10	<10	5.8	<5	0.72	2	111	1622	<1	5.55	0.02	25.60	1027	<2	0.01	2289	14	18	5	<0.01	15	<10	43
45494	<1	0.10	20	5.7	<5	0.48	2	110	1366	1	5.52	0.02	23.90	933	<2	0.01	2368	20	41	5	<0.01	16	<10	43
45495	<1	6.34	1484	8.5	<5	5.68	1	52	381	12	5.71	3.20	6.57	942	<2	1.21	269	2554	4	670	0.54	169	<10	58
45496	<1	0.14	<10	6.6	<5	0.19	2	105	1807	<1	6.54	0.04	23.50	766	<2	0.02	1877	34	16	11	0.01	19	<10	32
45497	<1	0.12	15	6.4	<5	0.42	2	115	1541	<1	6.27	0.03	24.50	873	<2	0.02	2289	22	23	12	<0.01	18	<10	35
45498	<1	0.09	<10	6.7	<5	0.02	2	114	1335	<1	6.38	0.03	24.19	838	<2	0.02	2244	21	19	2	<0.01	18	<10	30
45499	<1	0.10	<10	6.2	<5	0.10	2	109	1299	<1	5.99	0.03	23.33	809	<2	0.02	2222	20	14	3	<0.01	19	<10	31
45500	<1	2.10	129	6.0	<5	2.49	2	84	851	27	5.31	0.27	20.13	926	<2	0.03	1582	756	14	116	0.10	54	<10	37
Duplicates:																								
45401	<1	0.13	<10	5.4	<5	0.17	2	121	1505	4	5.48	0.01	26.58	1170	<2	0.02	2379	16	17	7	<0.01	15	<10	67
45410	<1	0.11	<10	6.1	<5	0.37	3	109	1471	17	6.10	<0.01	23.62	1015	<2	0.02	2353	21	23	10	<0.01	20	<10	81
45420	<1	0.09	<10	5.6	<5	0.10	2	104	956	<1	5.94	<0.01	25.53	795	<2	0.02	2342	19	11	1	<0.01	18	<10	23
45423	<1	0.10	<10	5.9	<5	0.12	2	103	1169	<1	6.00	0.01	26.62	792	<2	0.02	2455	13	12	2	<0.01	16	<10	20
45432	<1	0.08	<10	6.1	<5	0.07	3	96	1363	<1	6.17	<0.01	25.23	765	<2	0.02	2324	12	11	1	<0.01	17	<10	19
45442	<1	0.11	<10	5.5	<5	0.28	2	107	1293	<1	5.74	0.08	23.43	852	<2	0.02	2111	18	11	16	<0.01	19	<10	35
45445	<1	0.11	<10	5.7	<5	0.26	2	109	1553	<1	5.97	<0.01	23.01	859	<2	0.02	2239	27	14	11	<0.01	19	<10	40
45454	<1	0.07	<10	5.2	<5	0.19	2	105	1099	1	5.25	<0.01	23.09	564	<2	0.02	2330	23	12	16	<0.01	16	<10	21
45464	<1	9.44	486	8.4	<5	1.97	<1	48	37	33	7.78	1.38	4.31	2133	<2	3.35	27	843	239	497	0.51	358	<10	118
45467	<1	9.88	776	8.1	<5	1.68	<1	43	39	75	7.36	2.62	3.77	2171	<2	2.74	27	681	45	322	0.47	340	<10	156
45476	<1	0.06	<10	5.3	<5	1.33	2	99	847	26	5.48	0.01	22.65	934	<2	0.02	2330	19	7	11	<0.01	19	11	37
45486	<1	0.16	<10	5.1	<5	0.54	2	101	1038	6	5.06	<0.01	22.00	725	<2	0.01	2183	20	9	6	0.01	17	10	26
45489	<1	0.08	33	5.8	<5	0.20	2	118	1548	<1	5.54	0.01	24.90	975	<2	0.02	2429	26	20	5	<0.01	13	<10	38
45498	<1	0.09	<10	6.5	<5	0.02	2	114	1394	<1	6.46	0.03	24.24	843	<2	0.02	2276	29	15	2	<0.01	19	<10	29
Standards:																								
Blank	<1	0.01	<10	<0.5	<5	<0.01	<1	2	<1	<1	<0.01	<0.01	<0.01	<5	<2	0.01	<1	<10	<2	<1	<0.01	<1	<10	<2
CH-4	2	7.36	464	6.1	<5	1.91	2	33	92	1946	5.36	1.76	1.42	454	<2	3.11	63	643	13	202	0.30	97	<10	219

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V3176RR

Date : Dec-02-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
45501	<1	1.44	14	6.2	<5	0.38	2	97	1326	172	6.08	0.04	22.05	1109	<2	0.03	1877	165	14	95	0.09	82	<10	67
45502	<1	4.11	16	7.1	<5	0.85	2	82	1437	130	6.90	0.06	19.75	1586	<2	0.04	1208	430	11	113	0.23	174	<10	114
45503	<1	0.10	<10	5.2	<5	0.36	2	105	1375	7	5.11	<0.01	23.44	756	<2	0.02	2164	27	11	29	<0.01	17	<10	37
45504	<1	0.11	<10	5.5	<5	0.12	2	115	1460	5	5.42	<0.01	25.33	906	<2	0.02	2436	17	11	2	<0.01	16	<10	33
45505	<1	0.07	<10	5.9	<5	0.33	2	119	1350	1	5.96	<0.01	26.02	951	<2	0.01	2481	24	16	17	<0.01	16	<10	34
45506	<1	0.09	<10	5.7	<5	0.36	2	111	1636	1	5.72	<0.01	25.01	913	<2	0.01	2300	19	15	16	<0.01	15	<10	32
45507	<1	0.09	<10	5.7	<5	0.05	2	116	1263	<1	5.79	<0.01	26.17	921	<2	0.02	2493	14	12	1	<0.01	17	14	30
45508	<1	0.13	<10	5.7	<5	0.09	2	111	1451	1	5.61	<0.01	24.96	907	<2	0.02	2237	23	14	3	<0.01	20	<10	31
45509	<1	0.10	<10	5.8	<5	0.06	2	107	1211	5	5.59	<0.01	24.55	845	<2	0.02	2247	21	14	1	<0.01	18	<10	28
45510	<1	1.44	94	6.5	<5	0.69	2	80	1243	1	4.73	0.67	20.44	811	<2	0.58	1814	138	16	71	0.04	26	<10	25
45511	<1	0.35	39	5.3	<5	0.28	2	91	1152	14	5.06	0.05	22.38	739	<2	0.06	2239	72	13	54	0.01	25	<10	24
45512	<1	7.64	76	8.1	<5	2.15	1	67	455	10	7.76	0.22	14.29	1356	<2	0.14	648	796	<2	746	0.38	265	<10	40
45513	<1	8.94	23	7.8	<5	0.67	<1	49	124	<1	7.35	0.17	16.22	1625	<2	0.34	87	891	<2	50	0.49	291	<10	44
45514	<1	3.21	<10	6.3	<5	0.61	2	85	904	21	6.16	0.01	21.28	853	<2	0.04	1583	336	3	17	0.17	113	<10	26
45515	<1	8.08	458	6.8	<5	2.45	<1	59	228	15	6.36	1.01	12.31	1237	<2	0.99	334	942	2	555	0.39	247	<10	66
45516	<1	0.60	69	5.2	<5	1.28	2	102	1235	1	5.26	0.02	23.78	947	<2	0.03	2048	74	20	178	0.02	30	<10	28
45517	<1	0.13	<10	5.3	<5	0.57	2	107	1162	5	5.28	0.01	23.71	753	<2	0.02	2221	33	11	35	<0.01	17	<10	23
45518	<1	0.10	16	5.6	<5	0.73	2	109	1477	4	5.67	0.01	24.65	1389	<2	0.02	2336	20	14	29	<0.01	17	<10	37
45519	<1	0.11	<10	5.3	<5	0.23	2	107	2000	1	5.26	0.02	24.22	1027	<2	0.01	2291	28	17	16	<0.01	13	<10	38
45520	<1	0.10	<10	5.2	<5	0.23	2	108	1331	11	5.24	0.01	23.96	690	<2	0.02	2306	23	18	23	<0.01	16	<10	23
45521	<1	0.12	<10	5.2	<5	0.14	2	105	1278	7	5.26	0.01	24.54	737	<2	0.02	2208	20	15	7	<0.01	17	<10	22
45522	<1	0.11	<10	6.2	<5	0.26	2	110	1930	1	6.05	0.01	23.12	840	<2	0.01	2246	30	18	17	<0.01	17	<10	33
45523	<1	0.09	17	6.2	<5	0.11	2	109	1617	<1	6.04	0.01	24.41	889	<2	0.02	2162	14	22	4	<0.01	17	11	36
45524	<1	0.10	36	5.5	<5	0.23	2	112	1368	<1	5.55	<0.01	25.10	906	<2	0.02	2309	15	17	6	<0.01	17	<10	36
45525	<1	0.09	33	5.3	<5	0.20	2	110	1101	<1	5.42	0.01	25.58	830	<2	0.01	2358	18	18	3	<0.01	17	10	25
45526	<1	0.09	<10	5.9	<5	0.23	2	111	1450	<1	5.89	<0.01	24.55	949	<2	0.01	2284	16	19	8	<0.01	17	<10	36
45527	1	0.53	40	5.7	<5	1.63	8	91	926	8	5.22	0.08	20.18	1533	<2	0.03	1888	176	1269	97	0.04	28	<10	1562
45528	<1	7.78	1742	10.0	<5	2.50	1	57	388	<1	8.76	3.03	7.22	7471	<2	0.56	283	2832	104	419	0.62	185	<10	280
45529	<1	0.11	10	5.5	<5	0.59	2	103	1368	10	5.43	0.04	21.78	1099	<2	0.02	2002	23	27	40	<0.01	17	<10	84
45530	<1	0.17	11	5.9	<5	0.26	2	113	1808	<1	6.08	0.02	25.05	1059	<2	0.02	2257	36	25	10	0.01	20	<10	68

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V3176RR

Date : Dec-02-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
45531	<1	0.11	<10	5.1	<5	0.10	2	105	1082	<1	5.09	<0.01	25.33	855	<2	0.02	2287	18	19	4	<0.01	19	<10	37
45532	<1	0.12	<10	5.5	<5	0.11	2	110	1179	<1	5.57	0.01	26.03	931	<2	0.02	2281	14	17	2	<0.01	19	<10	33
45533	<1	0.10	<10	5.7	<5	0.13	2	108	1458	<1	5.65	<0.01	24.51	876	<2	0.01	2202	17	21	7	<0.01	16	<10	35
45534	<1	0.10	<10	6.0	<5	0.06	2	106	1357	<1	5.95	<0.01	24.37	819	<2	0.02	2169	16	16	2	<0.01	18	10	30
45535	<1	0.08	<10	5.3	<5	0.22	2	110	1125	<1	5.39	<0.01	25.49	986	<2	0.01	2375	18	30	7	<0.01	16	<10	44
45536	<1	0.12	<10	5.3	<5	0.06	2	105	1096	<1	5.30	<0.01	24.74	802	<2	0.02	2290	12	16	1	<0.01	20	<10	28
45537	<1	0.13	<10	5.6	<5	0.18	2	112	1493	<1	5.82	<0.01	25.31	934	<2	0.02	2363	23	17	2	<0.01	19	<10	33
45538	<1	0.16	<10	5.5	<5	0.20	2	105	1309	<1	5.44	0.01	24.70	858	<2	0.03	2185	25	15	2	<0.01	21	<10	34
45539	<1	0.15	<10	5.3	<5	0.20	2	103	1071	<1	5.26	0.01	24.37	829	<2	0.02	2211	18	21	4	<0.01	20	<10	30
45540	<1	0.13	<10	5.3	<5	0.28	2	103	1480	<1	5.29	<0.01	24.38	857	<2	0.02	2164	19	20	6	<0.01	18	<10	31
45541	<1	0.08	<10	5.3	<5	0.17	2	109	1163	<1	5.35	<0.01	25.08	892	<2	0.01	2280	16	17	6	<0.01	15	<10	29
45542	<1	0.10	<10	5.3	<5	0.11	2	106	1117	<1	5.31	0.01	25.06	852	<2	0.03	2264	27	21	5	<0.01	17	<10	29
45543	<1	0.08	<10	5.4	<5	0.23	2	107	1081	<1	5.43	<0.01	24.36	868	<2	0.02	2164	14	24	10	<0.01	16	<10	28
45544	<1	0.09	<10	5.7	<5	0.25	2	118	1449	<1	5.71	<0.01	26.24	1007	<2	0.02	2496	30	24	9	<0.01	17	<10	33
45545	<1	0.13	10	5.4	<5	0.13	4	106	1023	16	5.44	<0.01	23.53	866	<2	0.02	2082	15	39	8	<0.01	19	<10	380
45546	19	0.09	<10	5.6	20	0.17	25	106	994	134	5.32	<0.01	23.74	989	<2	0.02	2200	19	2369	6	<0.01	17	<10	5025
45547	<1	0.07	<10	5.4	<5	0.38	2	108	1479	<1	5.34	<0.01	23.49	911	<2	0.02	2206	15	30	18	<0.01	14	<10	55
45548	7	0.18	<10	7.5	<5	0.82	19	118	1164	368	7.22	<0.01	20.23	1314	<2	0.02	2107	15	919	40	<0.01	23	<10	3625
45549	<1	0.08	<10	5.5	<5	0.34	2	105	1326	3	5.40	<0.01	23.07	1107	<2	0.01	2101	14	22	14	<0.01	16	<10	50
45550	3	0.27	<10	5.7	<5	4.43	9	85	1041	98	5.31	<0.01	16.63	1958	<2	0.02	1761	54	129	778	0.01	18	<10	1609
45551	<1	0.13	<10	6.0	<5	0.41	3	101	1469	14	5.71	<0.01	21.58	1032	<2	0.02	1920	27	93	41	<0.01	17	<10	176
45552	<1	0.05	<10	5.6	<5	0.20	2	104	826	<1	5.62	<0.01	22.70	843	<2	0.01	2063	<10	13	9	<0.01	16	<10	31
45553	<1	0.12	<10	5.6	<5	0.43	2	96	833	<1	5.33	<0.01	22.19	1008	<2	0.02	2004	12	14	23	<0.01	16	<10	39
45554	<1	0.08	<10	5.2	<5	0.18	2	105	1093	<1	5.21	<0.01	23.75	838	<2	0.01	2107	14	13	9	<0.01	16	<10	27
45555	3	0.08	17	5.9	<5	1.52	2	107	963	<1	5.50	<0.01	22.36	1019	<2	0.01	2240	21	13	376	<0.01	17	<10	28
45556	<1	7.22	1838	7.5	<5	1.58	<1	25	141	22	4.46	3.87	4.00	1820	<2	1.69	97	2363	16	715	0.38	103	<10	120
45557	1	2.05	445	6.0	<5	3.05	5	80	784	5	4.82	0.98	15.26	1793	<2	0.28	1449	622	252	635	0.11	37	<10	841
45558	<1	7.65	1698	10.5	<5	0.99	2	23	135	1	8.74	2.96	4.62	6919	<2	0.56	74	2419	68	389	0.34	111	17	333
45559	<1	0.75	231	5.8	<5	1.84	2	91	763	<1	5.38	0.32	19.95	1488	<2	0.02	1754	226	18	129	0.02	26	<10	52
45560	<1	0.10	<10	5.4	<5	0.20	2	103	769	<1	5.28	<0.01	23.59	787	<2	0.01	2121	18	13	5	<0.01	18	<10	22

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

Assayers Canada
8282 Sherbrooke St., Vancouver, B.C., V5X 4R6
Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V3176RR
Date : Dec-02-08

ICP-AES Report
Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
45561	<1	0.05	<10	4.9	<5	0.17	2	108	746	<1	4.91	<0.01	24.24	806	<2	0.01	2224	12	11	5	<0.01	13	<10	18
45562	<1	0.04	<10	5.0	<5	0.14	2	100	755	<1	5.00	<0.01	24.01	812	<2	0.01	2232	11	14	7	<0.01	12	<10	18
45563	<1	0.07	<10	5.2	<5	0.15	2	101	896	<1	5.17	<0.01	23.86	786	<2	0.01	2175	<10	12	4	<0.01	16	<10	17
45564	<1	0.05	11	5.1	<5	0.18	2	103	1048	<1	5.01	<0.01	23.68	814	<2	0.01	2230	12	19	7	<0.01	11	<10	24
45565	<1	0.05	<10	5.2	<5	0.26	2	103	1146	<1	5.06	<0.01	23.94	796	<2	0.01	2174	12	13	9	<0.01	12	<10	19
45566	<1	0.09	<10	5.5	<5	0.24	2	104	1235	<1	5.40	<0.01	24.12	747	<2	0.02	2200	15	17	7	<0.01	16	<10	23
45567	<1	0.08	<10	5.2	<5	0.25	2	98	1041	<1	5.20	<0.01	23.10	712	<2	0.02	2084	21	17	8	<0.01	15	<10	15
45568	<1	0.09	<10	5.3	<5	0.16	2	100	933	<1	5.02	<0.01	23.50	690	<2	0.02	2139	28	14	8	<0.01	17	<10	14
45569	<1	0.09	<10	5.9	<5	0.31	2	106	1163	<1	5.75	<0.01	23.89	876	<2	0.02	2228	14	17	20	<0.01	17	<10	23
45570	<1	0.08	<10	5.2	<5	0.07	2	103	1090	<1	5.19	<0.01	23.52	750	<2	0.02	2135	<10	14	3	<0.01	15	<10	23
45571	<1	0.05	<10	5.9	<5	0.12	2	102	959	<1	5.97	<0.01	23.17	770	<2	0.01	2073	12	15	5	<0.01	15	<10	23
45572	<1	0.05	<10	5.3	<5	0.18	2	101	708	<1	5.07	<0.01	23.75	751	<2	0.01	2167	15	14	8	<0.01	13	<10	15
45573	<1	0.15	<10	4.0	<5	0.21	2	84	4411	<1	4.10	<0.01	20.88	847	<2	0.01	2034	<10	13	14	<0.01	3	<10	42
45574	<1	0.20	<10	2.8	<5	0.09	1	64	5129	<1	2.89	<0.01	19.61	703	<2	0.01	1943	11	8	6	<0.01	<1	<10	26
45575	<1	0.10	12	4.1	<5	0.21	2	85	3310	<1	4.15	<0.01	22.65	784	<2	0.01	2296	<10	18	7	<0.01	5	<10	23
45576	2	4.31	1230	6.9	<5	2.38	2	73	3205	35	5.81	1.63	12.65	1943	<2	0.77	1049	1399	179	457	0.33	96	<10	168
45577	<1	0.08	<10	5.6	<5	0.33	2	100	1936	<1	5.38	<0.01	23.22	915	<2	0.01	2155	12	18	9	<0.01	11	<10	15
45578	<1	0.08	<10	6.6	<5	0.37	3	106	1677	37	6.49	<0.01	22.45	784	<2	0.02	2229	15	18	6	<0.01	16	<10	16
45579	<1	0.08	<10	5.1	<5	0.08	2	98	1289	20	4.81	<0.01	22.47	614	<2	0.02	2084	10	14	3	<0.01	16	<10	18
45580	<1	0.06	<10	5.5	<5	0.22	2	103	796	54	5.34	<0.01	23.22	708	<2	0.01	2085	19	17	8	<0.01	17	<10	26
45581	<1	0.07	<10	5.1	<5	0.09	2	110	1393	39	4.96	<0.01	23.63	806	<2	0.02	2162	<10	10	2	<0.01	12	<10	25
45582	<1	0.03	<10	5.2	<5	0.19	2	104	850	2	5.09	<0.01	23.71	923	<2	0.01	2184	<10	12	5	<0.01	11	<10	20
45583	<1	0.03	<10	5.3	<5	0.17	2	113	984	15	5.22	<0.01	24.27	931	<2	0.01	2268	<10	14	6	<0.01	11	<10	23
45584	<1	0.04	<10	5.1	<5	0.12	2	105	968	5	4.88	<0.01	23.72	889	<2	0.01	2166	<10	11	2	<0.01	11	<10	23
45585	<1	0.05	33	5.6	<5	0.16	2	108	959	<1	5.37	<0.01	24.46	921	<2	0.01	2241	17	24	6	<0.01	13	<10	41
45586	<1	0.06	36	5.4	<5	0.42	2	104	925	8	5.16	<0.01	22.33	829	<2	0.01	2151	11	25	13	<0.01	15	<10	40
45587	<1	0.20	21	5.1	<5	0.75	2	101	1030	4	4.83	0.02	22.47	969	<2	0.02	2046	51	22	66	0.01	14	<10	37
45591	<1	0.29	37	7.3	<5	0.55	3	118	2759	<1	6.62	0.08	19.46	1047	<2	0.09	2502	50	31	23	0.01	19	<10	73
45592	<1	0.09	25	5.7	<5	3.23	2	99	1583	<1	5.32	0.01	20.10	940	<2	0.02	1898	24	25	63	<0.01	12	<10	46
45593	<1	0.08	51	5.7	<5	1.03	2	105	809	<1	5.48	0.01	22.18	790	<2	0.03	2157	26	34	21	<0.01	17	<10	40

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V3176RR

Date : Dec-02-08

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
45594	<1	0.78	111	6.1	<5	1.12	2	99	872	11	5.50	0.18	20.04	823	<2	0.12	1977	332	35	61	0.07	39	<10	42
45595	<1	0.07	10	5.6	<5	1.44	2	108	1022	<1	5.39	0.01	22.48	817	<2	0.02	2171	20	34	34	<0.01	16	<10	33
45596	<1	0.10	<10	5.4	<5	1.68	2	101	1447	<1	5.30	0.01	22.90	841	<2	0.02	2092	18	16	28	<0.01	16	<10	28
45597	<1	0.11	29	5.6	<5	1.95	2	104	1774	4	5.26	0.01	22.64	943	<2	0.02	2001	13	22	65	<0.01	16	<10	36
45598	<1	0.09	33	6.3	<5	0.95	2	119	1497	<1	6.19	0.01	25.07	951	<2	0.02	2383	26	32	57	<0.01	15	<10	36
45599	<1	0.10	10	6.4	<5	0.21	2	117	1669	<1	6.12	0.01	25.97	897	<2	0.02	2346	22	17	11	<0.01	16	<10	33
45600	<1	0.11	31	6.6	<5	0.35	3	120	1773	<1	6.50	0.01	25.49	924	<2	0.02	2409	20	28	13	<0.01	18	<10	38
Duplicates:																								
45501	<1	1.42	16	6.3	<5	0.37	2	98	1286	171	6.07	0.04	21.97	1103	<2	0.03	1871	168	16	93	0.09	82	<10	64
45510	<1	1.44	95	6.4	<5	0.69	2	81	1249	<1	4.73	0.72	20.25	808	<2	0.58	1793	135	12	70	0.04	26	<10	25
45520	<1	0.11	<10	5.2	<5	0.23	2	105	1231	13	5.23	0.01	23.92	692	<2	0.02	2314	23	15	22	<0.01	17	<10	25
45523	<1	0.10	18	6.2	<5	0.11	2	110	1712	<1	6.17	0.01	24.85	911	<2	0.02	2202	13	27	4	<0.01	17	<10	37
45532	<1	0.11	<10	5.4	<5	0.10	2	104	1312	<1	5.33	0.01	24.73	887	<2	0.02	2177	16	19	2	<0.01	18	<10	31
45542	<1	0.10	<10	5.3	<5	0.11	2	107	1176	2	5.32	0.01	25.02	848	<2	0.03	2270	27	21	5	<0.01	16	<10	30
45545	<1	0.13	10	5.4	<5	0.12	4	104	1391	14	5.19	<0.01	22.96	842	<2	0.02	2026	16	36	8	<0.01	17	<10	364
45554	<1	0.08	<10	5.3	<5	0.18	2	103	1036	<1	5.09	<0.01	23.46	824	<2	0.01	2100	<10	13	9	<0.01	16	<10	27
45564	<1	0.05	12	5.3	<5	0.18	2	107	1134	<1	5.20	<0.01	24.44	844	<2	0.01	2324	14	18	7	<0.01	11	<10	25
45567	<1	0.08	<10	5.2	<5	0.25	2	98	1037	<1	5.09	<0.01	22.79	703	<2	0.02	2060	<10	11	7	<0.01	15	<10	13
45576	2	4.23	1221	7.1	<5	2.34	2	71	3115	33	5.76	1.61	12.43	1925	<2	0.76	1043	1388	181	451	0.32	95	<10	168
45586	<1	0.07	37	5.4	<5	0.43	2	108	1015	5	5.38	<0.01	23.08	863	<2	0.02	2245	15	25	13	<0.01	16	<10	43
45592	<1	0.10	24	5.9	<5	3.32	2	102	1681	<1	5.45	0.01	20.62	968	<2	0.03	1949	31	25	65	<0.01	12	<10	49
Standards:																								
Blank	<1	0.01	<10	<0.5	<5	<0.01	<1	2	2	<1	0.02	<0.01	0.02	<5	<2	0.01	<1	<10	<2	<1	<0.01	<1	<10	<2
CH-4	2	7.72	493	6.8	<5	1.96	2	34	137	2041	5.73	1.83	1.46	475	<2	3.27	60	704	12	209	0.31	104	<10	219

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V3189RR

Date : Dec-05-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type: Core

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
45601	<1	0.12	<10	5.6	<5	0.12	2	120	1581	<1	6.06	0.01	26.07	937	<2	0.02	2458	<10	10	10	<0.01	18	<10	24
45602	<1	0.16	<10	5.3	<5	0.08	2	113	1343	<1	5.67	0.01	25.21	885	3	0.02	2330	39	5	7	<0.01	23	<10	23
45603	<1	0.14	<10	4.8	<5	0.38	2	108	1707	<1	5.22	<0.01	24.59	921	<2	0.02	2291	33	16	19	<0.01	19	<10	26
45604	<1	0.11	<10	5.1	<5	0.62	2	113	1329	<1	5.58	<0.01	24.32	1022	<2	0.02	2240	33	17	4	<0.01	19	<10	23
45605	<1	0.11	<10	5.0	<5	0.44	2	106	1465	<1	5.30	<0.01	23.53	907	<2	0.02	2233	29	9	16	<0.01	19	<10	25
45606	<1	0.10	<10	5.0	<5	1.33	2	100	1326	3	5.12	<0.01	22.28	1456	<2	0.02	2180	29	14	74	<0.01	16	<10	33
45607	<1	2.36	<10	6.2	<5	1.51	2	89	965	<1	6.28	0.01	19.32	2883	<2	0.02	1542	258	6	58	0.13	99	<10	108
45608	<1	0.11	<10	5.1	<5	<0.01	2	106	1071	<1	5.44	0.01	23.69	761	2	0.02	2207	16	13	2	<0.01	20	<10	24
45609	<1	0.08	<10	5.2	<5	<0.01	2	101	1103	<1	5.60	<0.01	22.98	797	4	0.02	2090	10	4	1	<0.01	20	16	23
45610	<1	0.12	<10	5.2	<5	0.01	2	113	1024	<1	5.68	<0.01	23.81	871	<2	0.02	2282	37	7	<1	<0.01	22	<10	24
45611	<1	0.13	<10	5.2	<5	<0.01	2	110	1080	<1	5.48	<0.01	23.61	840	<2	0.02	2261	18	13	<1	<0.01	21	12	26
45612	<1	0.13	<10	5.8	<5	<0.01	2	114	1572	<1	6.21	<0.01	23.79	897	2	0.02	2204	18	15	<1	<0.01	22	<10	32
45613	<1	0.10	<10	4.9	<5	0.17	2	106	1047	<1	5.49	0.01	24.21	778	<2	0.02	2217	31	20	5	<0.01	18	<10	25
45614	<1	0.24	<10	4.7	<5	0.44	2	104	1046	<1	5.08	0.01	22.83	891	<2	0.02	2142	29	13	24	<0.01	19	<10	39
45615	<1	0.77	72	6.2	<5	3.22	2	100	990	<1	6.40	0.01	20.47	2423	<2	0.02	1984	256	73	218	0.03	27	<10	93
45616	<1	8.13	2040	7.6	<5	1.70	1	25	108	17	4.21	4.27	2.90	2170	<2	2.32	53	2557	81	893	0.41	108	<10	153
45617	<1	8.09	1940	7.6	<5	2.45	<1	24	111	15	3.63	4.04	2.28	934	<2	3.01	40	2433	17	1041	0.45	102	<10	71
45618	<1	8.24	1978	7.8	<5	2.50	<1	26	115	14	3.91	4.10	2.45	944	<2	3.00	42	2632	11	1043	0.51	113	<10	76
45619	<1	8.53	1952	8.1	<5	3.31	<1	25	105	18	3.77	4.37	2.41	1063	2	2.98	32	2612	3	1113	0.47	108	<10	65
45620	<1	0.58	126	5.3	<5	0.82	2	107	1324	<1	5.50	0.27	23.01	906	<2	0.16	2112	179	19	121	0.03	25	<10	35
45621	<1	0.10	<10	4.8	<5	0.07	2	112	1242	<1	5.26	0.02	25.12	814	<2	0.02	2287	42	26	4	<0.01	17	<10	30
45622	1	0.08	<10	5.1	<5	0.03	2	113	1320	<1	5.75	0.01	25.26	870	2	0.02	2405	30	15	<1	<0.01	16	<10	29
45623	1	0.13	<10	5.1	<5	0.03	2	108	1483	<1	5.39	0.01	23.90	837	4	0.02	2130	36	<2	<1	<0.01	20	14	34
45624	<1	0.08	<10	4.8	<5	0.08	1	113	1156	<1	5.18	0.01	25.02	818	<2	0.02	2438	29	19	3	<0.01	15	11	30
45625	2	0.09	<10	4.1	<5	0.30	2	98	1082	51	4.40	0.01	22.04	759	3	0.02	2050	37	49	15	<0.01	15	14	37
45626	<1	0.10	<10	5.1	<5	0.04	2	111	1262	<1	5.63	0.01	24.66	839	<2	0.02	2279	33	11	2	<0.01	18	14	29
45627	1	0.05	<10	5.1	<5	0.27	2	110	908	<1	5.43	0.01	24.39	916	<2	0.01	2298	28	19	8	<0.01	15	<10	34
45628	<1	0.05	<10	6.2	<5	0.12	2	124	1106	<1	6.79	0.01	26.31	838	3	0.01	2605	44	21	10	<0.01	18	21	27
45629	<1	0.05	<10	5.5	<5	0.02	2	119	668	<1	5.88	0.01	26.47	968	<2	0.02	2492	28	21	2	<0.01	17	14	26
45630	2	0.14	<10	6.7	<5	0.06	2	151	1349	<1	7.76	0.04	33.81	1172	<2	0.03	3123	37	29	1	<0.01	24	18	43

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V3189RR

Date : Dec-05-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type: Core

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
45631	2	0.12	<10	6.4	<5	0.22	2	150	1713	<1	7.60	0.04	33.90	1307	3	0.04	3134	55	28	5	<0.01	24	12	51
45632	1	0.06	<10	5.3	<5	0.40	2	120	1288	<1	5.76	0.01	25.51	938	6	0.01	2417	29	20	6	<0.01	16	<10	39
45633	<1	0.03	<10	4.7	<5	<0.01	2	112	673	<1	5.28	<0.01	25.74	871	6	0.01	2373	25	14	<1	<0.01	14	<10	23
45634	1	0.02	<10	5.2	<5	0.09	2	117	652	<1	5.58	<0.01	25.59	822	2	0.01	2434	33	11	3	<0.01	15	<10	19
45635	1	0.04	<10	5.8	<5	0.37	2	118	1075	<1	6.29	<0.01	25.56	897	3	0.01	2425	41	20	4	<0.01	16	<10	20
45636	1	0.05	<10	5.0	<5	0.13	1	113	1241	<1	5.48	<0.01	25.47	918	<2	0.01	2280	15	14	<1	<0.01	14	<10	22
45637	<1	0.05	<10	5.5	<5	<0.01	2	118	991	<1	5.79	0.01	25.90	855	2	0.02	2446	29	5	<1	<0.01	18	16	21
45638	1	0.07	<10	5.4	<5	<0.01	1	118	1145	<1	5.86	0.01	26.41	934	<2	0.02	2385	13	16	<1	<0.01	18	<10	20
45639	2	0.05	<10	5.1	<5	<0.01	2	120	919	<1	5.33	0.01	26.23	900	4	0.01	2426	28	14	<1	<0.01	16	<10	20
45640	1	0.06	<10	5.3	<5	<0.01	2	131	1260	<1	6.05	0.02	29.87	1002	2	0.02	2766	39	23	<1	<0.01	16	12	25
45641	1	0.06	<10	5.1	<5	0.21	1	112	1079	<1	5.48	0.01	25.31	944	2	0.02	2402	32	20	5	<0.01	16	<10	36
45642	<1	0.07	<10	5.3	<5	0.42	2	115	1424	<1	5.61	0.01	24.77	982	3	0.01	2153	33	13	10	<0.01	18	14	28
45643	<1	0.07	<10	5.1	<5	0.50	2	111	1183	<1	5.52	0.01	23.82	1264	2	0.02	2243	30	30	17	<0.01	15	<10	31
45644	2	0.07	21	4.6	<5	0.04	1	114	805	<1	5.20	0.01	25.12	823	<2	0.02	2345	42	7	5	<0.01	16	10	25
45645	<1	0.04	<10	6.8	<5	0.24	2	117	1432	<1	7.07	<0.01	23.94	926	<2	0.01	2227	16	11	8	<0.01	17	<10	25
45646	<1	0.05	<10	5.4	<5	0.19	2	117	951	<1	5.72	0.01	24.71	838	<2	0.02	2404	30	19	25	<0.01	16	21	34
45647	<1	0.07	<10	5.1	<5	0.21	2	98	949	7	5.31	0.01	23.35	973	<2	0.02	2157	16	66	10	<0.01	15	<10	66
45648	<1	0.10	<10	5.3	<5	0.31	2	108	1114	1	5.47	0.01	23.70	1347	<2	0.02	2250	37	18	8	<0.01	17	<10	74
45649	1	0.10	<10	5.5	<5	0.03	2	110	1303	<1	5.83	0.01	24.45	946	<2	0.01	2213	20	10	1	<0.01	19	18	34
45650	<1	0.09	<10	5.5	<5	0.04	5	111	1067	18	5.65	0.01	25.26	966	<2	0.02	2351	19	38	2	<0.01	17	16	892
45651	<1	0.09	<10	6.0	<5	0.18	2	114	1049	<1	6.30	0.02	26.21	1026	<2	0.02	2236	35	15	3	<0.01	21	<10	63
45652	1	0.08	<10	5.3	<5	0.03	2	114	1048	<1	5.61	<0.01	25.25	871	<2	0.01	2287	<10	21	1	<0.01	18	<10	33
45653	<1	0.08	<10	6.3	<5	0.13	2	115	1456	<1	6.61	<0.01	24.14	927	<2	0.01	2251	28	7	2	<0.01	18	14	34
45654	<1	0.08	<10	5.7	<5	0.21	2	111	1143	<1	5.96	<0.01	23.79	874	<2	0.01	2179	16	9	4	<0.01	16	<10	28
45655	<1	0.07	<10	5.2	<5	0.40	2	98	1319	<1	5.31	<0.01	22.45	983	<2	0.02	2034	19	17	13	<0.01	16	<10	39
45656	<1	0.04	<10	5.3	<5	<0.01	1	113	1032	<1	5.66	<0.01	24.09	812	<2	0.01	2408	22	15	<1	<0.01	13	<10	25
45657	1	0.05	<10	4.9	<5	0.01	2	106	1592	4	5.19	<0.01	24.58	833	<2	0.01	2207	<10	10	<1	<0.01	12	<10	23
45658	<1	0.05	<10	5.2	<5	<0.01	2	114	1292	8	5.61	0.01	25.09	863	<2	0.01	2425	<10	15	<1	<0.01	13	<10	40
45659	1	0.11	<10	5.0	<5	0.15	1	109	1477	12	5.30	0.01	24.22	895	<2	0.02	2123	<10	7	3	<0.01	17	19	30
45660	<1	0.07	<10	5.4	<5	0.04	2	115	1304	<1	5.87	0.01	25.84	857	<2	0.02	2394	22	17	<1	<0.01	15	14	23

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type: Core

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V3189RR

Date : Dec-05-08

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
45661	1	0.07	<10	5.0	<5	0.28	2	112	960	<1	5.29	0.01	24.19	945	<2	0.01	2196	13	7	5	<0.01	15	17	25
45662	<1	0.11	<10	6.7	<5	0.92	2	96	2429	16	6.61	0.01	19.59	1715	<2	0.03	2135	34	84	31	<0.01	16	<10	111
45663	<1	0.08	<10	5.5	<5	0.05	2	110	1484	<1	5.82	0.01	24.70	788	<2	0.02	2325	20	18	2	<0.01	16	<10	26
45664	<1	0.07	<10	5.5	<5	<0.01	2	112	1133	<1	5.91	0.01	25.34	734	<2	0.02	2424	32	7	<1	<0.01	18	<10	32
45665	<1	0.06	<10	5.2	<5	0.02	2	105	1151	<1	5.69	0.01	25.40	724	<2	0.01	2378	10	7	<1	<0.01	15	10	14
45666	<1	0.28	<10	3.6	<5	0.05	1	71	8737	<1	3.88	<0.01	20.22	1010	<2	0.01	1992	28	<2	<1	0.01	3	<10	35
45667	<1	0.32	<10	4.7	<5	<0.01	1	81	>10000	<1	4.79	<0.01	22.40	976	<2	0.02	2250	<10	11	<1	0.01	<1	<10	3
45668	<1	0.20	<10	5.3	<5	<0.01	2	93	6346	<1	5.41	<0.01	24.41	905	<2	0.01	2334	20	8	<1	0.01	10	<10	7
45669	2	0.07	<10	5.4	<5	<0.01	2	113	1393	<1	5.52	0.01	26.84	826	<2	0.02	2547	18	11	<1	<0.01	16	<10	16
45670	1	0.04	<10	5.4	<5	<0.01	2	120	1227	<1	5.68	<0.01	27.53	881	<2	0.01	2633	16	12	<1	<0.01	17	<10	14
45671	<1	0.94	17	6.6	<5	0.03	2	112	742	<1	5.71	0.41	22.71	843	<2	0.45	2277	57	3	17	0.03	21	<10	30
45672	<1	0.09	<10	5.4	<5	0.50	2	115	874	<1	5.57	0.01	25.47	923	<2	0.02	2485	18	3	32	<0.01	16	<10	23
45673	<1	0.05	<10	5.5	<5	0.01	2	112	868	<1	5.59	<0.01	24.60	867	<2	0.01	2379	<10	6	4	<0.01	14	<10	21
45674	<1	0.09	<10	5.2	<5	0.39	2	111	966	<1	5.44	<0.01	25.04	874	<2	0.01	2102	<10	9	36	<0.01	16	<10	18
45675	<1	0.10	<10	5.8	<5	0.02	2	113	1033	<1	5.81	<0.01	25.71	801	<2	0.01	2412	<10	3	2	<0.01	17	<10	19
45676	1	0.04	<10	6.2	<5	0.03	2	121	953	<1	6.32	<0.01	25.73	893	<2	0.01	2435	22	<2	3	<0.01	14	<10	22
45677	<1	0.04	<10	5.7	<5	0.08	2	124	1777	<1	5.76	<0.01	25.68	927	<2	0.01	2416	<10	3	4	<0.01	11	<10	23
45678	2	0.04	<10	5.6	<5	<0.01	2	111	1348	<1	5.80	<0.01	25.01	850	<2	0.01	2340	<10	5	1	<0.01	12	<10	21
45679	<1	0.06	<10	5.9	<5	<0.01	2	116	2428	<1	6.19	<0.01	25.23	883	<2	0.01	2392	11	12	1	<0.01	10	<10	25
45680	<1	0.07	<10	5.2	<5	0.08	2	115	2252	<1	5.43	<0.01	26.12	907	<2	0.01	2335	15	4	3	<0.01	9	<10	24
45681	<1	0.03	<10	4.9	<5	<0.01	2	109	843	<1	5.13	<0.01	25.55	829	<2	0.01	2457	18	8	1	<0.01	10	<10	16
45682	1	0.06	<10	5.3	<5	0.12	2	113	1307	<1	5.49	<0.01	25.35	912	<2	0.01	2206	20	8	3	<0.01	11	15	25
45683	<1	0.03	<10	5.2	<5	<0.01	2	110	899	<1	5.48	<0.01	25.39	856	<2	0.01	2419	<10	7	<1	<0.01	12	10	20
45684	<1	0.04	<10	5.4	<5	0.10	2	121	1294	<1	5.48	<0.01	25.14	968	<2	0.01	2534	19	13	3	<0.01	12	13	23
45685	1	0.07	<10	5.4	<5	0.28	2	113	1042	<1	5.42	0.01	25.10	966	<2	0.02	2338	14	12	3	<0.01	15	<10	34
45686	1	0.06	<10	5.3	<5	0.25	2	116	737	<1	5.37	<0.01	24.94	793	<2	0.01	2388	16	12	<1	<0.01	15	17	22
45687	<1	0.03	<10	5.6	<5	3.61	2	119	1257	57	5.89	<0.01	23.19	1877	<2	0.01	1783	11	13	75	<0.01	12	<10	41
45688	1	0.03	<10	5.9	<5	0.04	2	127	710	<1	5.86	<0.01	25.49	859	<2	0.01	2386	<10	5	3	<0.01	13	<10	26
45689	<1	0.09	10	<0.5	<5	0.05	6	138	932	5	7.12	0.01	26.51	908	<2	0.02	2264	<10	4	2	0.01	8	<10	46
45690	<1	0.14	<10	<0.5	<5	0.76	6	132	1715	184	6.46	0.01	24.14	1255	<2	0.02	2101	<10	13	11	0.01	12	<10	61

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type: Core

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V3189RR

Date : Dec-05-08

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
45691	2	0.12	<10	<0.5	<5	0.28	6	138	1066	1007	5.75	0.01	24.69	1110	<2	0.02	2126	<10	15	6	0.01	13	<10	54
45692	<1	0.09	<10	<0.5	<5	0.34	6	140	930	449	6.71	0.01	26.97	972	<2	0.02	2208	<10	6	4	0.01	12	<10	49
45693	<1	0.14	<10	<0.5	<5	0.41	5	113	1252	22	5.68	0.01	23.74	1188	<2	0.02	2102	<10	6	12	0.01	12	<10	51
45694	<1	0.14	<10	<0.5	<5	0.70	6	118	1330	5	5.93	0.01	23.50	1430	<2	0.02	2091	13	8	28	0.01	13	<10	51
45695	<1	0.10	<10	<0.5	<5	0.76	5	114	908	2	5.59	0.01	24.62	1321	<2	0.02	2087	<10	31	46	0.01	11	<10	56
45696	<1	0.16	<10	<0.5	<5	0.48	5	119	1054	2	5.62	0.01	23.33	1413	<2	0.02	2110	<10	6	29	0.01	13	<10	52
45697	<1	0.17	11	<0.5	<5	0.87	4	88	832	<1	4.81	0.01	22.38	1202	<2	0.03	1754	13	8	87	<0.01	13	<10	66
45698	<1	0.14	37	<0.5	<5	4.06	5	117	1266	2	5.41	0.01	19.68	1663	2	0.03	2031	<10	5	1183	<0.01	15	<10	53
45699	1	9.27	267	2.1	<5	1.10	9	57	649	<1	14.23	0.77	10.57	>10000	<2	0.27	578	3167	53	79	0.21	137	21	401
45700	1	8.72	2184	3.3	<5	0.80	4	37	167	14	8.93	2.72	4.86	6658	<2	1.05	76	4386	132	421	0.33	149	19	261
Duplicates:																								
45601	<1	0.11	<10	5.4	<5	0.11	2	115	1154	<1	5.89	0.01	25.06	902	2	0.02	2383	42	22	10	<0.01	18	<10	25
45610	<1	0.11	<10	5.3	<5	0.02	2	112	950	<1	5.72	0.01	24.12	885	<2	0.02	2319	15	15	<1	<0.01	20	<10	24
45620	<1	0.56	121	5.4	<5	0.79	2	108	1233	<1	5.39	0.25	22.40	885	<2	0.16	2089	166	12	118	0.03	23	<10	35
45623	<1	0.13	<10	5.0	<5	0.03	2	108	1227	<1	5.46	0.01	24.30	846	6	0.03	2150	31	11	<1	<0.01	21	12	33
45632	1	0.06	<10	5.3	<5	0.40	2	120	1288	<1	5.76	0.01	25.51	938	6	0.01	2417	29	20	6	<0.01	16	<10	39
45642	<1	0.07	<10	5.2	<5	0.43	2	115	1456	<1	5.63	0.01	25.04	989	2	0.02	2206	35	13	10	<0.01	17	<10	28
45645	<1	0.04	<10	6.7	<5	0.26	3	122	1298	<1	7.31	0.01	24.64	956	<2	0.01	2298	28	16	8	<0.01	17	13	33
45654	<1	0.08	<10	5.6	<5	0.21	2	114	1144	<1	6.01	0.01	24.03	885	<2	0.01	2171	15	12	4	<0.01	18	<10	28
45664	<1	0.07	<10	5.2	<5	<0.01	2	105	1233	<1	5.60	<0.01	24.18	695	<2	0.02	2277	23	<2	<1	<0.01	16	16	24
45667	1	0.39	<10	5.1	<5	<0.01	2	89	>10000	<1	5.10	<0.01	22.69	1055	<2	0.01	2306	<10	9	<1	0.01	<1	21	14
45676	<1	0.04	<10	6.1	<5	0.04	2	118	1220	<1	6.37	<0.01	25.78	897	<2	0.01	2413	13	10	3	<0.01	14	<10	22
45686	1	0.06	<10	5.1	<5	0.25	2	113	740	<1	5.26	<0.01	24.32	770	<2	0.01	2300	11	10	<1	<0.01	14	<10	24
45689	<1	0.06	<10	<0.5	<5	0.04	6	141	894	10	6.92	0.01	25.57	900	<2	0.02	2181	<10	<2	2	<0.01	7	<10	42
45698	<1	0.12	36	<0.5	<5	4.04	5	117	1291	1	5.33	0.01	19.55	1660	2	0.02	2046	<10	4	1203	<0.01	15	<10	53
Standards:																								
Blank	<1	0.01	<10	<0.5	<5	<0.01	<1	2	4	<1	0.02	<0.01	<0.01	<5	<2	0.01	1	<10	<2	<1	<0.01	<1	<10	<2
CH-4	2	7.92	488	6.1	<5	1.97	2	36	217	2050	5.66	1.89	1.54	485	<2	3.35	67	707	11	215	0.33	105	16	215

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V3328RR

Date : Oct-29-08

WHY Resources

Attention: Dave MacKinnon

Project: Record Ridge South

Sample type: Rock

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
45717	<1	6.09	1139	5.2	<5	1.50	2	46	624	11	5.02	3.34	7.19	1080	2	2.37	602	1352	68	649	0.29	71	<10	85
45718	<1	0.19	35	<0.5	<5	0.09	7	133	1162	4	8.49	0.06	26.31	1090	<2	0.05	2323	33	22	16	0.01	17	<10	52
45719	<1	0.11	12	<0.5	<5	0.20	5	113	1559	3	6.62	0.01	24.98	1080	<2	0.02	2010	<10	23	8	<0.01	12	<10	60
45720	<1	0.31	38	0.5	<5	0.66	5	114	1514	2	6.12	0.06	22.63	972	<2	0.03	2053	94	24	50	0.02	13	<10	56
45721	<1	2.41	510	1.6	<5	0.98	4	95	1177	8	6.79	1.13	19.17	1220	2	0.47	1368	782	38	256	0.15	39	<10	58
45722	<1	0.06	<10	<0.5	<5	0.30	5	118	881	9	6.44	0.01	25.89	1065	<2	0.02	1981	<10	20	10	<0.01	10	<10	39
45723	<1	0.08	10	<0.5	<5	0.28	5	117	1257	20	6.43	0.01	25.66	1010	<2	0.02	2125	<10	21	13	<0.01	9	<10	48
45724	<1	0.08	<10	<0.5	<5	0.26	5	117	1028	9	5.94	0.01	26.78	1127	<2	0.02	2016	<10	14	12	<0.01	9	<10	43
45725	<1	0.05	<10	<0.5	<5	0.12	5	116	1034	14	6.44	0.01	26.01	1077	<2	0.02	2121	<10	19	3	<0.01	8	<10	39
45726	<1	0.08	<10	<0.5	<5	0.12	5	110	1083	8	6.31	0.01	26.11	1022	<2	0.02	2023	<10	19	4	<0.01	9	<10	41
45727	<1	0.08	<10	<0.5	<5	0.21	6	115	1083	3	6.90	0.01	26.21	1015	<2	0.01	1854	<10	21	7	<0.01	9	<10	40
45728	<1	0.07	<10	<0.5	<5	0.12	5	118	1150	2	5.72	0.01	26.20	952	<2	0.02	2001	<10	13	2	<0.01	7	<10	35
45729	<1	0.06	<10	<0.5	<5	0.18	4	113	1237	2	5.23	0.01	27.42	1020	<2	0.02	2045	<10	21	3	<0.01	6	<10	38
45730	<1	0.11	<10	<0.5	<5	0.16	5	121	3073	2	6.71	0.01	27.01	1166	<2	0.02	2070	<10	17	2	<0.01	4	<10	64
45731	<1	0.09	<10	<0.5	<5	0.03	5	114	1081	1	6.24	0.01	27.76	1074	<2	0.02	2033	<10	13	1	<0.01	9	<10	34
45732	<1	0.06	<10	<0.5	<5	0.25	5	124	1417	1	7.09	0.01	29.60	1120	<2	0.02	2097	<10	13	3	<0.01	8	<10	45
45733	<1	0.06	<10	<0.5	<5	0.27	7	132	1641	1	8.28	0.01	27.65	1205	<2	0.02	2295	<10	14	4	<0.01	8	<10	52
45734	<1	0.06	<10	<0.5	<5	0.35	6	129	1679	2	8.17	0.01	27.07	1152	<2	0.02	2259	<10	6	6	<0.01	8	<10	48
45735	<1	0.06	<10	<0.5	<5	0.18	5	116	1298	5	6.02	0.01	26.90	1077	<2	0.02	2085	<10	10	8	<0.01	7	<10	46
45736	<1	0.12	<10	<0.5	<5	0.24	5	101	939	13	5.71	0.03	23.87	964	<2	0.08	1987	<10	15	13	<0.01	13	<10	42
45737	<1	1.84	554	0.7	<5	1.24	3	87	1179	17	5.25	0.80	19.12	1126	2	0.28	1366	734	42	282	0.15	47	<10	91
45738	<1	0.17	<10	<0.5	<5	0.14	5	109	1847	2	6.57	0.01	26.47	1178	<2	0.02	1976	<10	23	8	<0.01	16	<10	72
45739	<1	0.11	10	<0.5	<5	0.56	6	122	1663	4	6.46	0.01	25.93	1360	<2	0.03	1990	<10	20	37	<0.01	14	<10	110
45740	<1	3.32	750	1.7	<5	2.14	4	88	1524	9	6.60	1.18	18.89	1633	2	1.02	1087	1274	64	379	0.26	83	<10	138
45741	<1	8.27	2539	4.2	<5	5.34	2	47	248	18	6.68	4.35	6.13	2937	3	1.21	83	3548	263	914	0.67	209	<10	238
45742	<1	0.21	25	<0.5	<5	0.47	5	117	1516	5	6.41	0.03	27.67	1217	<2	0.04	2052	39	20	30	0.01	18	<10	88
45743	<1	0.13	14	<0.5	<5	0.55	6	117	1444	4	7.18	0.02	27.91	1119	<2	0.03	1974	<10	9	32	0.01	16	<10	86
45744	<1	0.11	<10	<0.5	<5	0.57	6	127	1581	2	6.84	0.01	29.07	1149	<2	0.03	2173	<10	7	10	<0.01	16	<10	70
45745	<1	0.11	<10	<0.5	<5	0.20	5	117	1533	4	6.19	0.01	29.17	1116	<2	0.03	1891	<10	5	5	<0.01	14	<10	69
45746	<1	0.10	<10	<0.5	<5	0.16	5	126	1606	2	6.34	0.01	29.08	1089	<2	0.02	2046	<10	7	4	<0.01	16	<10	73

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

WHY Resources

Report No : 8V3328RR

Date : Oct-29-08

ICP-AES Report

Multi-Acid Digestion

A .2 gm sample is digested with HNO₃/HClO₄/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V3328RR

Date : Oct-29-08

WHY Resources

Attention: Dave MacKinnon

Project: Record Ridge South

Sample type: Rock

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
45777	<1	0.13	<10	<0.5	<5	0.04	6	124	2189	1	6.52	0.01	28.87	1229	<2	0.03	2118	<10	2	1	<0.01	16	<10	68
45778	<1	0.13	<10	<0.5	<5	0.03	6	124	1798	1	6.47	0.01	29.36	1205	<2	0.03	2168	<10	3	<1	<0.01	17	<10	65
45779	<1	0.12	<10	<0.5	<5	0.21	6	122	2227	1	6.43	0.01	27.51	1232	<2	0.02	1951	13	9	4	<0.01	14	<10	78
45780	<1	0.11	<10	<0.5	<5	0.46	6	139	1665	1	7.05	0.01	27.79	1445	2	0.02	2213	<10	11	7	<0.01	15	<10	81
45781	<1	0.07	<10	<0.5	<5	0.13	6	127	1189	1	6.37	0.02	27.78	1204	<2	0.02	2215	<10	12	4	<0.01	13	<10	61
45782	<1	0.09	<10	<0.5	<5	0.07	6	122	1262	1	6.52	0.01	28.29	1202	<2	0.02	2120	<10	12	1	<0.01	15	<10	57
45783	<1	0.14	<10	<0.5	5	0.05	4	85	1201	10	4.79	<0.01	20.69	883	<2	0.01	1797	15	16	1	<0.01	12	<10	30
45784	<1	0.16	<10	<0.5	7	0.66	5	116	1807	1	7.06	0.01	25.34	1364	<2	0.02	2173	42	46	14	<0.01	17	<10	71
45785	<1	0.15	<10	<0.5	<5	0.38	4	79	1244	3	4.53	<0.01	18.88	862	<2	0.01	1651	17	15	15	<0.01	12	<10	32
45786	<1	0.13	<10	<0.5	<5	0.14	4	79	941	1	3.96	<0.01	19.87	831	<2	0.01	1618	20	17	8	<0.01	11	<10	27
45787	<1	0.15	<10	<0.5	<5	0.27	4	79	1259	2	4.20	<0.01	18.95	865	<2	0.02	1665	25	16	18	<0.01	11	<10	34
45788	<1	0.14	<10	<0.5	<5	0.18	5	88	1360	1	4.99	<0.01	19.54	972	<2	0.01	1822	22	12	14	<0.01	11	<10	30
45789	<1	0.12	<10	<0.5	<5	0.44	5	89	1110	5	4.97	<0.01	18.74	998	<2	0.01	1828	18	11	17	<0.01	12	<10	32
45790	<1	0.11	<10	<0.5	<5	0.52	4	117	1427	5	5.74	0.01	25.34	1195	<2	0.02	2260	26	21	17	<0.01	13	<10	53
45791	<1	0.18	<10	<0.5	<5	0.14	4	84	1278	10	4.50	<0.01	19.25	858	<2	0.01	1712	16	10	9	<0.01	14	<10	30
45792	<1	0.17	<10	<0.5	5	0.16	5	85	1289	10	4.98	<0.01	19.02	934	<2	0.01	1686	19	10	13	<0.01	14	<10	30
45793	<1	0.14	<10	<0.5	<5	0.14	4	85	1187	3	4.42	<0.01	19.41	939	<2	0.01	1773	19	10	17	<0.01	12	<10	30
45794	<1	0.13	<10	<0.5	5	0.18	4	85	1014	7	4.29	<0.01	19.57	906	<2	0.01	1692	25	16	21	<0.01	12	<10	27
45795	<1	0.15	<10	<0.5	5	0.06	5	91	1172	3	4.83	<0.01	20.43	849	<2	0.01	1769	15	12	2	<0.01	13	<10	25
45796	<1	0.12	<10	<0.5	5	0.12	6	97	1047	3	5.74	<0.01	19.78	942	<2	0.01	1949	16	21	5	<0.01	13	<10	25
45797	<1	0.12	<10	<0.5	5	0.09	5	96	1346	<1	5.15	<0.01	21.07	954	<2	0.01	1933	22	9	3	<0.01	10	<10	31
45798	<1	0.13	<10	<0.5	5	0.11	5	96	1517	<1	5.18	<0.01	20.42	942	<2	0.01	1948	14	9	3	<0.01	9	<10	32
45799	<1	0.13	<10	<0.5	5	0.14	5	95	1344	<1	5.18	<0.01	20.36	915	<2	0.01	1929	30	15	5	<0.01	10	<10	31
45800	<1	0.09	11	<0.5	5	0.03	5	91	779	<1	4.46	<0.01	20.84	878	<2	0.01	1788	15	13	1	<0.01	8	<10	23

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V3313RR

Date : Dec-16-08

WHY Resources

Attention: Mitchell Marasco

Project: Record Ridge South

Sample type: Rock

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
45801	<1	0.16	18	<0.5	10	0.18	5	130	1372	1	6.60	0.02	31.16	1282	<2	0.03	2277	10	16	6	0.01	12	<10	28
45802	<1	0.07	10	<0.5	10	0.09	5	133	666	1	5.96	0.01	33.84	1239	<2	0.02	2422	<10	16	3	<0.01	8	<10	23
45803	<1	0.11	<10	<0.5	11	0.39	5	130	1711	<1	7.07	<0.01	29.97	1278	<2	0.01	2088	<10	14	5	<0.01	8	<10	30
45804	<1	0.14	<10	<0.5	11	0.07	4	129	1982	<1	6.52	<0.01	31.32	1168	<2	0.02	2350	<10	12	1	<0.01	10	<10	36
45805	<1	0.15	10	<0.5	12	0.04	5	134	1744	<1	6.63	<0.01	33.30	1099	<2	0.02	2473	<10	16	1	<0.01	12	<10	36
45806	<1	0.11	<10	<0.5	11	0.23	5	125	1203	<1	6.54	<0.01	29.79	1019	<2	0.01	2165	<10	16	1	<0.01	9	<10	26
45807	2	0.07	<10	<0.5	10	0.36	4	132	954	1	5.81	<0.01	32.77	1082	<2	0.01	2335	<10	10	2	<0.01	8	<10	22
45808	<1	0.08	<10	<0.5	12	0.26	6	141	1207	2	8.11	<0.01	30.94	1151	<2	0.01	2362	<10	12	3	<0.01	11	<10	29
45809	<1	0.10	<10	<0.5	10	0.33	5	131	1063	1	6.48	<0.01	31.34	1061	<2	0.01	2332	<10	7	9	<0.01	11	<10	24
45810	<1	0.18	<10	<0.5	10	0.07	3	126	2692	<1	5.95	<0.01	29.80	1045	<2	0.02	2263	<10	8	3	<0.01	13	<10	45
45811	<1	0.19	<10	<0.5	13	0.34	5	137	3048	1	7.82	<0.01	30.63	1317	<2	0.02	2400	<10	10	10	0.01	13	<10	45
45812	<1	0.11	<10	<0.5	11	0.08	4	127	1958	<1	6.35	<0.01	30.68	1080	<2	0.02	2324	<10	8	1	<0.01	10	<10	30
45813	<1	0.09	<10	<0.5	9	0.10	4	131	1561	<1	6.39	<0.01	31.17	1047	<2	0.02	2360	<10	7	2	<0.01	9	<10	27
45814	<1	0.10	<10	<0.5	10	0.17	4	135	1468	<1	6.50	<0.01	31.96	1072	<2	0.01	2463	<10	8	6	<0.01	9	<10	26
45815	<1	0.13	<10	<0.5	10	0.15	5	135	1569	<1	6.78	<0.01	32.45	1192	<2	0.02	2392	<10	12	3	<0.01	12	<10	45
45830	<1	0.18	11	<0.5	9	0.80	5	123	1297	<1	6.51	<0.01	28.29	1082	<2	0.03	2196	<10	13	37	<0.01	18	<10	31
45831	<1	0.14	<10	<0.5	10	0.73	4	119	1601	1	6.31	<0.01	28.21	1218	<2	0.02	2091	<10	5	73	<0.01	14	<10	46
45832	<1	0.13	<10	<0.5	10	0.25	4	124	1564	<1	6.46	<0.01	29.41	1083	<2	0.02	2198	<10	10	9	<0.01	13	<10	33
45833	<1	0.15	<10	<0.5	12	0.71	5	128	1467	<1	6.57	<0.01	29.80	1607	<2	0.02	2244	<10	9	28	<0.01	14	<10	43
45834	<1	0.12	<10	<0.5	10	0.65	4	119	1357	1	6.32	<0.01	26.73	1533	<2	0.02	2035	<10	12	25	<0.01	14	<10	43
45835	<1	0.12	<10	<0.5	11	0.18	4	122	1758	<1	6.50	<0.01	29.50	969	<2	0.02	2107	<10	9	11	<0.01	9	<10	34
45836	<1	0.17	<10	<0.5	11	0.30	5	127	1722	<1	6.80	<0.01	28.94	953	<2	0.03	2202	<10	6	18	<0.01	17	<10	36
45837	<1	0.09	<10	<0.5	<5	0.29	5	115	1191	1	6.09	0.01	27.77	1040	<2	<0.01	2043	<10	<2	7	<0.01	10	<10	38
45838	<1	0.10	<10	<0.5	<5	0.75	5	113	1311	2	6.29	0.01	27.27	1070	<2	<0.01	2003	<10	<2	23	<0.01	11	<10	44
45839	<1	1.78	11	<0.5	<5	0.45	5	99	849	28	6.21	0.02	24.17	975	<2	0.01	1659	229	<2	11	0.08	54	<10	55
45840	<1	0.15	<10	<0.5	<5	0.65	5	109	1121	5	5.64	0.01	26.87	936	<2	0.02	1947	<10	<2	8	<0.01	14	<10	43
45841	<1	0.14	18	<0.5	<5	1.62	5	108	1191	3	5.68	0.01	27.57	1060	<2	0.01	1979	<10	<2	52	<0.01	14	<10	52
45842	<1	0.14	10	<0.5	<5	0.58	5	109	1351	3	5.96	0.01	27.97	950	<2	0.02	1995	<10	<2	16	<0.01	14	<10	48
45843	<1	0.15	10	<0.5	<5	0.20	5	117	1711	2	6.07	0.01	27.17	986	<2	0.02	2067	<10	<2	9	<0.01	14	<10	47
45844	<1	0.14	41	<0.5	<5	0.40	6	125	2251	11	7.40	0.01	27.77	1110	<2	<0.01	1915	<10	<2	22	<0.01	10	<10	55

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V3313RR

Date : Dec-16-08

WHY Resources

Attention: Mitchell Marasco

Project: Record Ridge South

Sample type: Rock

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
45845	<1	0.12	11	<0.5	<5	0.28	5	119	1881	4	6.35	0.01	28.27	1010	<2	0.01	2035	<10	<2	13	<0.01	10	<10	49
45846	<1	0.12	<10	<0.5	<5	0.47	6	121	1401	2	6.56	0.02	27.87	913	<2	0.01	2107	<10	<2	16	<0.01	12	<10	43
45847	<1	0.14	<10	<0.5	<5	0.34	5	105	1271	5	6.04	0.01	25.67	877	<2	0.01	1755	<10	<2	6	<0.01	12	<10	36
45848	<1	0.10	<10	<0.5	<5	0.27	6	119	1051	7	6.34	0.01	25.97	907	<2	0.01	2051	<10	<2	8	<0.01	11	<10	31
45849	<1	0.12	<10	<0.5	<5	0.11	5	114	1461	5	6.53	0.01	26.77	814	<2	0.01	1923	<10	<2	10	<0.01	11	<10	33
45850	<1	0.11	<10	<0.5	<5	0.33	5	109	1111	5	6.04	<0.01	25.57	767	<2	0.01	1931	<10	<2	9	<0.01	12	<10	31
45851	<1	0.10	<10	<0.5	<5	0.25	5	114	1301	9	6.04	0.01	28.07	886	<2	0.01	2035	<10	<2	9	<0.01	9	<10	32
45852	<1	0.10	<10	<0.5	<5	0.43	5	115	1481	5	5.93	0.01	27.27	858	<2	<0.01	2003	<10	<2	10	<0.01	7	<10	40
45853	<1	0.08	<10	<0.5	<5	0.12	5	110	898	10	5.75	<0.01	27.77	794	<2	<0.01	1987	<10	<2	3	<0.01	7	<10	28
45854	<1	0.12	<10	<0.5	<5	0.40	5	107	1341	8	5.75	0.01	27.47	943	<2	0.01	1875	<10	<2	8	<0.01	9	<10	30
45855	<1	0.12	<10	<0.5	<5	0.75	5	112	1741	6	6.20	0.01	26.77	959	<2	0.01	1939	<10	<2	13	<0.01	9	<10	37
45856	<1	0.09	<10	<0.5	<5	0.12	5	114	1021	7	5.45	<0.01	27.87	894	<2	0.01	2035	<10	<2	3	<0.01	8	<10	28
45857	<1	0.08	<10	<0.5	<5	0.08	5	114	811	6	6.05	0.01	29.27	856	<2	0.01	2091	<10	<2	3	<0.01	8	<10	29
45858	<1	0.08	<10	<0.5	<5	0.11	5	119	878	8	5.89	0.01	28.27	855	<2	0.01	2139	<10	<2	4	<0.01	8	<10	28
45859	<1	0.10	<10	<0.5	8	0.37	4	115	1568	9	6.03	0.01	28.47	1032	<2	0.02	1769	<10	8	4	<0.01	11	<10	25
45860	<1	0.08	<10	<0.5	8	0.07	4	115	1124	9	6.02	0.01	29.05	967	<2	0.03	1863	<10	15	2	<0.01	9	<10	23
45861	<1	0.08	<10	<0.5	7	0.19	4	116	957	31	5.83	0.01	28.80	901	<2	0.02	1934	<10	15	4	<0.01	10	<10	20
45862	<1	0.11	<10	<0.5	7	0.47	4	113	1432	76	6.20	0.01	27.86	1097	<2	0.04	1832	<10	20	18	<0.01	13	<10	38
45863	<1	0.11	<10	<0.5	7	0.30	4	123	1199	20	6.26	0.01	29.45	1023	<2	0.04	1852	<10	11	6	<0.01	12	<10	31
45864	<1	0.15	18	<0.5	8	0.11	4	118	1371	23	6.74	0.01	28.89	949	<2	0.03	1854	<10	10	2	<0.01	16	<10	32
45865	<1	0.15	<10	<0.5	8	0.10	4	118	1669	25	6.35	0.01	29.89	989	<2	0.03	1954	<10	18	1	<0.01	14	<10	35
45866	<1	0.11	<10	<0.5	7	0.08	4	123	1679	24	6.24	0.01	29.32	986	<2	0.02	2058	<10	15	1	<0.01	12	<10	34
45867	<1	0.12	<10	<0.5	8	0.18	4	131	1876	17	6.24	<0.01	29.55	1032	<2	0.02	1987	<10	12	3	<0.01	11	<10	38
45868	<1	0.11	<10	<0.5	5	1.14	2	103	1505	11	5.03	<0.01	26.72	1341	<2	0.02	1661	31	15	35	<0.01	11	<10	46
45869	<1	0.11	<10	<0.5	7	0.26	3	124	1984	12	6.47	0.01	28.20	1025	<2	0.03	1838	<10	20	5	<0.01	12	<10	41
45870	<1	0.09	<10	<0.5	7	0.07	4	121	1389	9	6.72	<0.01	29.15	893	<2	0.02	2012	<10	9	2	<0.01	13	<10	30
45871	<1	0.11	<10	<0.5	7	0.19	5	122	1811	10	7.53	<0.01	28.44	1001	<2	0.02	1951	<10	10	2	<0.01	14	<10	33
45872	<1	0.09	<10	<0.5	7	0.08	4	120	1109	9	6.12	0.01	29.26	912	<2	0.02	2040	<10	14	2	<0.01	12	<10	32
45873	<1	0.14	<10	<0.5	6	0.19	4	116	1593	10	6.18	0.01	28.72	958	<2	0.03	1912	<10	15	5	<0.01	16	<10	33
45874	<1	0.10	<10	<0.5	6	0.19	4	112	1280	3	6.23	0.01	28.02	839	<2	0.02	1909	<10	18	4	<0.01	13	<10	25

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V3313RR

Date : Dec-16-08

WHY Resources

Attention: Mitchell Marasco

Project: Record Ridge South

Sample type: Rock

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
45875	<1	0.10	<10	<0.5	6	0.27	4	118	1509	2	6.46	<0.01	27.07	901	<2	0.03	1776	<10	21	10	<0.01	13	<10	29
45876	<1	0.12	<10	<0.5	7	0.80	3	128	2100	1	5.74	0.01	27.64	1130	<2	0.03	1708	<10	12	21	<0.01	9	<10	46
45877	<1	0.14	<10	<0.5	7	0.18	3	116	1858	2	6.18	0.01	27.75	993	<2	0.04	1798	<10	9	2	<0.01	10	<10	43
45878	<1	0.13	<10	<0.5	6	0.13	3	120	1303	3	5.84	0.01	27.59	875	<2	0.03	1857	<10	9	2	<0.01	13	<10	34
45879	<1	0.14	<10	<0.5	6	0.47	3	117	1967	5	5.68	0.01	26.93	1458	<2	0.02	1850	<10	12	13	<0.01	12	<10	54
45880	<1	0.12	<10	<0.5	7	0.61	4	131	1825	6	6.60	<0.01	28.08	1059	<2	0.02	1995	<10	10	12	<0.01	13	<10	47
45881	<1	0.14	<10	<0.5	10	0.54	4	125	1961	8	6.91	0.01	27.88	1208	<2	0.03	2152	<10	9	10	0.01	11	<10	36
45882	<1	0.15	<10	<0.5	9	0.19	4	120	1756	5	6.89	0.01	27.58	1008	<2	0.03	2041	<10	6	4	<0.01	14	<10	34
45883	<1	0.14	<10	<0.5	10	0.32	4	120	1389	4	6.52	0.01	28.44	926	<2	0.03	2033	<10	3	6	<0.01	12	<10	25
45884	<1	0.14	<10	<0.5	9	0.14	4	117	1296	2	6.54	0.01	28.35	947	<2	0.03	2075	<10	2	2	<0.01	13	<10	27
45885	<1	0.17	<10	<0.5	10	0.26	4	119	1362	3	6.61	0.01	29.01	933	<2	0.04	2096	<10	5	5	<0.01	16	<10	33
45886	<1	0.17	11	<0.5	8	0.15	4	116	1530	<1	6.68	<0.01	26.83	879	<2	0.02	2050	<10	5	4	<0.01	17	<10	36
45887	<1	0.14	<10	<0.5	9	0.24	3	110	1812	<1	5.83	<0.01	27.73	905	<2	0.02	1981	<10	5	2	<0.01	13	<10	27
45888	<1	0.11	<10	<0.5	9	0.07	4	120	1113	<1	6.43	<0.01	28.61	877	<2	0.02	2091	<10	2	2	<0.01	12	<10	19
45889	<1	0.13	<10	<0.5	11	0.04	5	115	1450	<1	6.60	<0.01	27.74	933	<2	0.02	2014	<10	<2	1	<0.01	13	<10	21
45890	<1	0.09	<10	<0.5	11	0.19	5	126	1490	<1	7.04	<0.01	28.28	914	<2	0.02	2125	<10	2	5	<0.01	10	<10	20
45891	<1	0.11	<10	<0.5	11	0.32	4	117	1518	1	6.13	<0.01	28.09	943	<2	0.02	2116	<10	<2	10	<0.01	11	<10	27
45892	<1	0.11	<10	<0.5	11	0.27	5	114	1525	2	6.26	<0.01	27.44	1101	<2	0.02	1997	<10	16	7	0.01	10	<10	54
45893	<1	0.09	<10	<0.5	11	0.20	5	112	1415	<1	6.09	<0.01	27.37	943	<2	0.02	1957	<10	3	6	<0.01	9	<10	27
45894	<1	0.12	<10	<0.5	13	0.19	4	116	2029	<1	6.26	<0.01	27.60	938	<2	0.02	1993	<10	2	4	<0.01	10	<10	54
45895	<1	0.14	<10	<0.5	11	0.62	4	113	1590	<1	6.28	<0.01	27.36	934	<2	0.02	1996	<10	<2	19	<0.01	12	<10	28
45896	<1	0.09	<10	<0.5	12	1.65	4	103	1314	<1	5.67	<0.01	28.60	1533	<2	0.02	1706	<10	14	62	<0.01	8	<10	40
45897	<1	0.07	<10	<0.5	11	0.17	5	122	1422	<1	6.30	<0.01	29.05	966	<2	0.01	2098	<10	7	6	<0.01	7	<10	30
45898	<1	0.12	<10	<0.5	12	0.31	4	113	1393	<1	6.18	0.01	28.19	981	<2	0.03	2025	<10	4	7	<0.01	11	<10	34
45899	<1	0.13	<10	<0.5	11	0.29	5	116	1292	<1	6.89	<0.01	27.63	935	<2	0.03	2000	<10	6	10	<0.01	11	<10	33
45900	<1	0.14	<10	<0.5	12	0.31	5	110	1514	<1	6.27	<0.01	27.52	915	<2	0.02	1923	<10	2	8	<0.01	12	<10	29
Duplicates:																								
45801	<1	0.16	16	<0.5	12	0.18	4	128	1788	<1	6.58	0.02	30.14	1269	<2	0.03	2246	<10	8	6	0.01	11	<10	32
45810	<1	0.19	<10	<0.5	10	0.07	3	126	2734	2	6.16	<0.01	29.97	1051	<2	0.02	2261	<10	6	3	<0.01	13	<10	47
45834	<1	0.13	<10	<0.5	10	0.64	4	115	1437	1	6.18	<0.01	26.38	1501	<2	0.02	1983	<10	7	25	<0.01	13	<10	44

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V3313RR

Date : Dec-16-08

WHY Resources

Attention: Mitchell Marasco

Project: Record Ridge South

Sample type: Rock

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
45837	<1	0.11	<10	<0.5	<5	0.29	5	118	1311	2	6.09	0.01	27.67	1060	<2	0.01	2075	<10	<2	8	<0.01	10	<10	38
45846	<1	0.12	<10	<0.5	<5	0.44	5	113	1241	2	6.08	0.02	25.77	867	<2	0.02	1979	<10	<2	15	<0.01	12	<10	39
45856	<1	0.10	<10	<0.5	<5	0.11	5	110	730	8	5.51	0.01	28.17	868	<2	0.02	1963	<10	<2	3	<0.01	8	<10	25
45859	<1	0.10	<10	<0.5	6	0.38	3	125	1405	10	6.32	<0.01	28.87	1073	<2	0.02	1813	<10	14	5	<0.01	12	<10	28
45868	<1	0.12	<10	<0.5	6	1.15	3	107	1648	10	5.21	0.01	26.92	1381	<2	0.03	1715	28	14	36	<0.01	12	<10	52
45878	<1	0.13	<10	<0.5	6	0.13	3	118	1886	3	6.05	<0.01	28.29	911	<2	0.03	1947	<10	15	3	<0.01	13	<10	38
45881	<1	0.13	<10	<0.5	12	0.51	5	121	1673	5	6.66	<0.01	27.73	1179	<2	0.02	2086	<10	6	10	<0.01	11	<10	28
45890	<1	0.08	<10	<0.5	12	0.18	5	119	1175	<1	6.74	<0.01	27.77	885	<2	0.01	2021	<10	2	5	<0.01	10	<10	20
45900	<1	0.13	<10	<0.5	12	0.32	5	113	1810	<1	6.30	<0.01	27.82	931	<2	0.01	1985	<10	3	8	<0.01	11	<10	25
Standards:																								
Blank	<1	<0.01	<10	<0.5	<5	<0.01	<1	<1	<1	<1	<0.01	<0.01	<0.01	<5	<2	<0.01	<1	<10	<2	<1	<0.01	<1	<10	<2
CH-4	2	7.72	499	1.3	<5	1.99	3	34	90	1990	5.59	1.74	1.54	479	2	3.05	52	828	23	197	0.33	95	10	217

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V3324RR

Date : Dec-05-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
45901	<1	0.13	<10	6.1	<5	0.04	2	110	1429	<1	5.64	0.01	24.23	819	<2	0.03	2117	17	17	5	<0.01	20	<10	32
45902	<1	0.10	<10	5.9	<5	<0.01	2	106	1085	<1	5.49	0.01	24.34	837	<2	0.02	1987	17	11	2	<0.01	18	<10	25
45903	<1	0.09	<10	6.4	<5	0.09	2	116	1466	<1	5.99	<0.01	24.76	894	<2	0.01	2145	14	14	3	<0.01	20	<10	29
45904	<1	0.10	<10	5.9	<5	0.15	2	109	1468	<1	5.68	0.01	25.29	876	<2	0.02	2039	20	16	11	<0.01	19	<10	28
45905	<1	0.09	<10	6.6	<5	0.13	2	118	1718	<1	5.96	<0.01	25.71	927	<2	0.01	2204	<10	17	3	<0.01	18	<10	30
45906	<1	0.09	<10	6.6	<5	0.10	2	121	1683	<1	6.19	<0.01	27.37	992	<2	0.01	2278	<10	17	3	<0.01	18	<10	31
45907	<1	0.09	<10	6.8	<5	0.12	2	118	1598	<1	6.17	<0.01	25.81	909	<2	0.02	2201	14	14	2	<0.01	19	<10	29
45908	<1	0.09	<10	6.2	<5	0.09	2	114	1502	<1	5.68	<0.01	25.83	927	<2	0.01	2186	11	18	3	<0.01	18	<10	28
45909	<1	0.10	<10	6.1	<5	0.18	2	112	1137	<1	5.47	<0.01	26.23	914	<2	0.01	2120	12	18	6	<0.01	20	<10	25
45910	<1	0.08	<10	6.2	<5	0.11	2	113	860	<1	5.64	<0.01	25.74	837	<2	0.01	2132	<10	16	4	<0.01	19	<10	27
45911	<1	0.09	<10	6.7	<5	0.09	2	118	1572	<1	6.20	<0.01	25.83	901	<2	0.01	2162	12	16	2	<0.01	20	<10	29
45915	<1	0.31	<10	6.7	<5	1.78	2	108	1218	5	5.54	<0.01	20.66	2211	<2	0.02	1728	19	85	183	<0.01	19	<10	134
45916	<1	0.08	<10	6.4	<5	0.38	2	120	1611	<1	5.83	<0.01	24.31	1065	<2	0.01	2210	39	16	23	<0.01	16	<10	32
45917	<1	0.05	<10	6.2	<5	0.61	2	115	1348	1	5.59	<0.01	23.81	1088	<2	0.01	2079	19	24	69	<0.01	11	<10	26
45918	1	0.04	<10	6.5	<5	0.26	2	118	1194	<1	5.77	<0.01	24.09	1059	<2	0.01	2125	17	16	15	<0.01	12	<10	28
45919	<1	0.03	<10	6.4	<5	<0.01	2	117	1252	<1	5.78	<0.01	24.86	1081	<2	0.01	2157	15	17	1	<0.01	11	<10	23
45920	<1	0.03	<10	5.8	<5	0.70	2	110	1039	<1	5.37	<0.01	23.99	1236	<2	0.01	2059	10	15	40	<0.01	11	<10	30
45921	<1	0.03	<10	6.2	<5	0.83	2	110	1021	<1	5.63	<0.01	23.47	1336	<2	0.01	2008	15	20	35	<0.01	11	<10	36
45922	<1	0.03	<10	5.9	<5	0.03	2	115	809	<1	5.39	<0.01	25.34	1040	<2	0.01	2142	<10	23	2	<0.01	11	<10	26
45923	<1	0.03	<10	6.1	<5	0.24	2	115	966	<1	5.62	<0.01	24.33	931	<2	0.01	2143	18	18	4	<0.01	13	<10	27
45924	<1	0.06	<10	5.8	<5	0.59	2	109	934	<1	5.19	<0.01	23.35	960	<2	0.01	2025	17	15	18	<0.01	15	<10	26
45925	<1	0.09	<10	5.8	<5	0.15	2	109	947	<1	5.43	<0.01	25.29	873	<2	0.01	2038	<10	18	1	<0.01	18	<10	25
45926	<1	0.08	<10	5.4	<5	0.40	2	106	1261	<1	5.28	<0.01	23.28	872	<2	0.01	1886	17	18	29	<0.01	16	<10	33
45927	<1	0.07	<10	6.4	<5	0.23	2	109	1462	<1	5.98	<0.01	23.88	902	<2	0.01	2079	14	17	4	<0.01	19	<10	32
45928	<1	0.09	<10	6.4	<5	0.12	2	109	1554	<1	5.81	<0.01	24.06	868	<2	0.01	1984	10	14	1	<0.01	19	<10	27
45929	<1	0.12	<10	5.9	<5	0.24	2	106	1724	<1	5.52	<0.01	23.86	900	<2	0.01	1958	<10	10	4	<0.01	20	<10	37
45930	<1	0.11	<10	6.4	<5	0.15	2	115	1675	<1	5.88	<0.01	24.08	906	<2	0.01	1950	11	46	3	<0.01	19	<10	36
45931	<1	0.07	<10	6.3	<5	0.21	2	109	1249	<1	5.75	<0.01	23.83	859	<2	0.01	2013	10	22	10	<0.01	18	<10	37
45932	<1	0.11	<10	5.9	<5	0.33	2	102	1370	1	5.49	0.01	23.29	830	<2	0.02	1972	18	17	23	<0.01	20	<10	37
45933	<1	0.11	<10	5.3	<5	0.72	2	97	1387	<1	4.91	<0.01	23.29	986	<2	0.01	1833	16	16	29	<0.01	19	<10	34

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V3324RR

Date : Dec-05-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
45934	<1	0.11	<10	6.1	<5	0.04	2	110	1230	<1	5.68	<0.01	25.08	900	<2	0.02	2114	<10	13	<1	<0.01	23	<10	30
45935	<1	0.13	<10	6.1	<5	<0.01	2	112	1389	<1	5.69	<0.01	25.40	853	<2	0.02	2082	10	10	<1	<0.01	23	<10	27
45936	<1	0.14	<10	5.9	<5	<0.01	2	108	1359	<1	5.55	<0.01	25.02	797	<2	0.02	2120	10	7	<1	<0.01	22	<10	27
45937	<1	0.13	<10	5.8	<5	0.20	2	106	1421	<1	5.55	<0.01	24.53	836	<2	0.02	2041	12	11	16	<0.01	22	10	29
45938	<1	0.12	<10	6.1	<5	0.35	2	109	1502	<1	5.72	<0.01	23.42	930	<2	0.02	1972	15	12	26	<0.01	23	<10	30
45939	<1	0.11	<10	6.1	<5	0.02	2	113	1686	<1	5.73	<0.01	24.72	872	<2	0.02	2051	12	14	2	<0.01	20	<10	30
45940	<1	0.11	<10	6.4	<5	0.59	2	114	1644	<1	6.02	<0.01	25.57	1068	<2	0.02	2066	11	14	14	<0.01	21	<10	35
45941	<1	0.13	<10	6.3	<5	<0.01	2	111	1548	<1	5.84	<0.01	25.22	884	<2	0.02	2047	<10	9	<1	<0.01	22	<10	27
45942	<1	0.08	<10	6.6	<5	0.04	2	112	1402	<1	6.02	<0.01	25.26	910	<2	0.01	2116	<10	12	<1	<0.01	19	<10	26
45943	<1	0.09	<10	6.8	<5	0.35	2	123	1503	<1	6.24	<0.01	25.58	1101	<2	0.01	1816	<10	13	2	<0.01	18	<10	29
45944	<1	0.08	<10	6.7	<5	0.02	2	115	1487	<1	6.14	<0.01	24.84	881	<2	0.01	2106	<10	11	<1	<0.01	20	<10	28
45945	<1	0.09	<10	5.8	<5	0.34	2	106	1153	<1	5.60	<0.01	23.91	801	<2	0.01	2101	14	9	17	<0.01	20	<10	26
45946	<1	0.13	<10	6.6	<5	0.01	2	112	1550	<1	6.15	<0.01	24.17	803	<2	0.02	2065	13	14	2	<0.01	25	<10	28
45947	<1	0.10	<10	6.3	<5	<0.01	2	114	1200	<1	5.95	<0.01	25.47	878	<2	0.02	2056	10	14	<1	<0.01	21	<10	26
45948	<1	0.13	<10	6.2	<5	0.23	2	120	2768	<1	5.77	<0.01	24.10	1088	<2	0.01	2042	18	15	7	0.01	19	<10	58
45949	<1	0.09	<10	6.5	<5	0.05	2	112	1470	<1	5.99	<0.01	25.53	901	<2	0.01	2138	11	9	<1	<0.01	18	<10	30
45950	<1	0.09	<10	6.2	<5	0.01	2	118	2430	<1	5.76	<0.01	25.36	1058	<2	0.01	2108	16	9	1	<0.01	16	<10	57
45951	<1	0.08	<10	6.6	<5	0.26	2	120	1434	<1	6.33	<0.01	25.11	995	<2	0.01	1929	14	14	4	<0.01	17	<10	33
45952	<1	0.09	<10	6.2	<5	0.63	2	96	1796	<1	5.62	<0.01	20.94	911	<2	0.02	1469	26	14	27	<0.01	19	<10	68
45953	<1	0.09	<10	6.2	<5	0.40	2	112	1415	<1	5.78	<0.01	24.14	866	<2	0.01	2008	15	13	15	<0.01	19	10	31
45954	<1	0.10	<10	6.1	<5	0.07	2	110	1085	<1	5.61	<0.01	24.73	838	<2	0.02	2105	<10	12	2	<0.01	17	<10	29
45955	<1	0.11	<10	6.2	<5	0.03	2	116	1378	<1	5.81	<0.01	25.83	986	<2	0.02	2173	12	13	<1	<0.01	19	<10	36
45956	<1	0.09	<10	5.9	<5	0.41	2	111	1169	<1	5.53	<0.01	24.62	1022	<2	0.01	1869	12	11	10	<0.01	20	<10	35
45957	<1	0.06	<10	6.4	<5	0.06	2	116	1203	<1	6.01	<0.01	24.33	807	<2	0.01	2125	12	12	4	<0.01	18	<10	29
45958	<1	0.11	<10	6.2	<5	0.02	2	117	2744	<1	5.91	<0.01	25.12	1106	<2	0.01	2135	11	26	1	<0.01	17	<10	50
45959	<1	0.13	<10	6.4	<5	0.31	2	110	4409	<1	5.88	<0.01	24.13	1197	<2	0.01	2015	16	11	8	<0.01	13	<10	75
45960	<1	0.19	<10	6.0	<5	0.67	2	109	1361	<1	5.82	0.01	23.92	1301	<2	0.01	2043	14	183	17	<0.01	18	13	117
45961	<1	0.08	<10	6.2	<5	0.26	2	118	1517	<1	5.99	0.01	23.85	991	<2	0.02	2139	16	17	12	<0.01	17	<10	36
45962	<1	0.10	<10	6.1	<5	0.92	2	102	1188	<1	5.93	0.01	22.75	834	<2	0.02	1856	31	21	84	<0.01	19	<10	37
45963	<1	0.08	<10	6.3	<5	0.08	2	113	1420	<1	6.09	0.01	24.80	890	<2	0.02	2072	13	11	4	<0.01	20	<10	34

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V3324RR

Date : Dec-05-08

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
45964	<1	3.20	750	7.7	<5	2.28	5	81	1233	15	6.21	1.41	15.83	1116	<2	0.95	1219	1159	143	445	0.26	86	<10	182
45965	<1	0.10	<10	6.3	<5	0.12	2	117	1601	<1	5.89	0.02	25.72	1020	<2	0.03	2246	11	30	6	<0.01	18	11	54
45966	<1	0.10	<10	6.5	<5	0.03	2	109	1229	<1	6.05	0.01	24.72	847	<2	0.02	2064	12	11	2	<0.01	19	<10	36
45967	<1	0.08	<10	6.2	<5	0.55	2	115	1212	<1	5.86	0.01	26.61	1054	<2	0.01	2070	10	38	6	<0.01	18	<10	47
45968	<1	0.08	<10	5.9	<5	0.51	2	115	1101	<1	5.64	0.01	25.31	925	<2	0.02	2138	10	20	10	<0.01	17	<10	40
45969	<1	0.06	<10	6.3	<5	0.27	2	115	1084	<1	5.93	0.01	26.17	1019	<2	0.01	2189	14	26	2	<0.01	15	<10	40
45970	<1	0.11	<10	6.3	<5	0.37	2	112	1634	<1	5.84	0.02	25.84	988	<2	0.02	2108	18	9	12	<0.01	17	<10	35
45971	<1	0.10	<10	6.3	<5	0.69	2	114	1195	<1	5.74	0.01	25.38	967	<2	0.01	2153	12	10	6	<0.01	17	<10	33
45972	<1	0.06	<10	6.1	<5	0.61	2	116	1013	<1	5.63	0.01	26.77	1057	<2	0.01	2190	15	7	12	<0.01	16	<10	37
45973	<1	1.52	320	6.9	<5	1.15	2	100	833	<1	5.85	0.32	21.99	924	<2	0.41	1815	535	7	295	0.12	48	<10	31
45974	<1	0.09	<10	5.7	<5	1.32	2	108	1095	<1	5.27	<0.01	23.62	938	<2	0.02	2047	18	12	61	<0.01	18	<10	48
45975	<1	0.10	<10	6.1	<5	0.38	2	106	1295	<1	5.76	<0.01	24.66	956	<2	0.02	1927	18	28	13	<0.01	18	<10	50
45976	<1	0.08	<10	6.6	<5	0.25	2	119	1367	<1	6.21	<0.01	27.09	983	<2	0.01	2251	11	9	9	<0.01	17	<10	35
45977	<1	0.06	<10	6.5	<5	0.17	2	118	813	<1	6.07	<0.01	26.57	954	<2	0.01	2230	16	8	6	<0.01	16	<10	29
45978	<1	0.06	<10	6.5	<5	0.19	2	122	941	<1	6.11	<0.01	27.23	1006	<2	0.01	2328	12	10	3	<0.01	17	<10	31
45979	<1	0.04	<10	6.4	<5	0.14	2	119	707	<1	5.99	<0.01	26.74	1017	<2	0.02	2251	13	11	4	<0.01	16	<10	29
45980	<1	0.05	<10	5.9	<5	0.56	2	102	838	2	5.36	<0.01	23.70	1173	<2	0.02	1992	22	20	14	<0.01	15	<10	47
45981	<1	0.06	<10	6.0	<5	0.06	2	113	985	<1	5.68	<0.01	26.05	826	<2	0.01	2200	15	11	2	<0.01	16	<10	27
45982	<1	0.07	<10	6.1	<5	0.15	2	112	1249	2	5.83	<0.01	25.81	883	<2	0.02	2145	15	16	3	<0.01	17	<10	138
45983	<1	0.07	<10	6.8	<5	0.11	2	117	1271	<1	6.34	<0.01	26.23	902	<2	0.02	2278	14	15	2	<0.01	18	<10	26
45984	<1	0.08	<10	7.3	<5	<0.01	2	123	1638	<1	6.80	<0.01	26.68	889	<2	0.02	2238	14	11	<1	<0.01	19	<10	25
45985	<1	0.07	<10	6.2	<5	0.02	2	119	1110	<1	5.88	<0.01	27.44	899	<2	0.01	2313	11	11	<1	<0.01	16	<10	25
45986	<1	0.08	<10	7.2	<5	<0.01	2	125	1578	<1	6.73	<0.01	27.51	962	<2	0.02	2422	18	9	<1	<0.01	19	<10	30
45987	<1	0.17	<10	6.0	<5	0.31	2	111	1119	<1	5.78	<0.01	22.24	843	<2	0.02	2129	31	7	13	<0.01	23	<10	28
45988	<1	0.11	<10	5.9	<5	0.36	2	106	1012	2	5.56	<0.01	23.58	886	<2	0.01	1998	17	10	11	<0.01	19	<10	27
45989	<1	0.12	<10	6.2	<5	0.95	2	99	1290	49	5.74	<0.01	23.01	1050	<2	0.01	1860	28	9	117	<0.01	21	<10	39
45990	<1	0.09	<10	5.8	<5	1.12	2	101	1012	116	5.40	<0.01	22.78	897	<2	0.01	1991	20	7	84	<0.01	18	<10	25
45991	<1	0.13	<10	5.9	<5	1.43	2	107	1196	139	5.74	0.01	22.60	897	<2	0.02	1954	16	9	68	<0.01	24	<10	29
45992	<1	0.15	<10	5.9	<5	0.94	2	102	1173	3	5.44	0.01	23.31	877	<2	0.02	1953	16	9	40	<0.01	22	<10	24
45993	<1	0.09	<10	6.1	<5	0.65	2	111	1014	<1	5.73	0.01	23.97	826	<2	0.02	2107	30	13	24	<0.01	19	<10	26

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V3324RR

Date : Dec-05-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type:

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
45994	<1	0.11	<10	5.4	<5	0.96	2	94	1018	<1	5.15	<0.01	22.67	989	<2	0.01	1781	27	13	69	<0.01	18	<10	29
45995	<1	0.09	<10	5.9	<5	1.09	2	108	1139	<1	5.56	<0.01	23.80	1326	<2	0.01	1969	16	10	107	<0.01	18	<10	29
45996	<1	0.07	<10	6.7	<5	0.69	2	113	1091	<1	6.20	<0.01	24.66	1091	<2	0.01	2014	16	12	15	<0.01	17	<10	28
45997	<1	0.04	<10	6.0	<5	0.85	2	112	971	<1	5.76	<0.01	24.21	1101	<2	0.01	2093	20	13	34	<0.01	14	<10	31
45998	<1	0.06	<10	6.6	<5	1.32	2	124	1073	6	6.31	<0.01	23.92	1104	<2	0.02	2060	19	16	82	<0.01	17	<10	31
45999	<1	9.32	14	9.7	<5	0.27	1	69	263	186	8.53	0.01	17.76	3236	<2	0.41	446	876	74	23	0.48	329	<10	152
46000	<1	0.38	<10	5.6	<5	1.59	2	98	1006	14	5.30	0.01	21.35	1383	<2	0.02	1737	61	54	153	0.02	24	<10	61
Duplicates:																								
45901	<1	0.13	<10	6.0	<5	0.03	2	106	1440	<1	5.54	0.01	23.86	807	<2	0.02	2036	19	21	4	<0.01	19	<10	29
45910	<1	0.08	<10	6.1	<5	0.11	2	112	892	<1	5.59	<0.01	25.47	825	<2	0.01	2129	11	17	3	<0.01	20	<10	26
45923	<1	0.02	<10	6.3	<5	0.25	2	119	818	<1	5.89	<0.01	25.27	963	<2	0.01	2244	22	21	5	<0.01	13	<10	27
45926	<1	0.08	<10	5.5	<5	0.40	2	103	1184	<1	5.25	<0.01	23.15	869	<2	0.01	1864	15	19	29	<0.01	17	<10	34
45935	<1	0.13	<10	5.9	<5	<0.01	2	105	1307	<1	5.48	<0.01	24.74	827	<2	0.02	2040	<10	11	<1	<0.01	21	<10	26
45945	<1	0.09	<10	6.0	<5	0.35	2	107	1045	<1	5.49	<0.01	23.86	797	<2	0.01	2082	18	15	17	<0.01	20	<10	25
45948	<1	0.13	<10	6.5	<5	0.25	2	123	2296	<1	5.98	<0.01	25.79	1153	<2	0.01	2157	21	20	8	<0.01	20	<10	55
45957	<1	0.06	<10	6.5	<5	0.07	2	120	1196	<1	6.25	<0.01	25.29	846	<2	0.01	2222	14	12	4	<0.01	18	<10	30
45967	<1	0.08	<10	6.1	<5	0.55	2	115	1181	<1	5.76	0.01	26.46	1049	<2	0.01	2028	<10	32	6	<0.01	17	<10	46
45970	<1	0.11	<10	6.2	<5	0.37	2	112	1522	<1	5.89	0.01	26.17	998	<2	0.02	2126	12	11	12	<0.01	18	<10	34
45979	<1	0.04	<10	6.5	<5	0.14	2	120	832	<1	6.11	0.01	27.14	1029	<2	0.01	2258	17	14	3	<0.01	16	<10	30
45989	<1	0.13	<10	6.1	<5	0.98	2	103	1305	50	5.90	0.01	23.68	1072	<2	0.01	1892	31	13	121	<0.01	21	<10	39
45992	<1	0.15	<10	5.7	<5	0.95	2	101	1146	5	5.52	0.01	23.54	889	<2	0.02	1980	19	13	39	<0.01	21	<10	25
*10 DUP.	<1	8.29	1033	5.8	<5	2.56	<1	14	213	4	3.09	2.87	1.54	874	<2	2.56	53	926	9	724	0.28	69	<10	64
Standards:																								
Blank	<1	<0.01	<10	<0.5	<5	<0.01	<1	2	3	<1	0.01	<0.01	0.02	<5	<2	0.01	1	<10	<2	<1	<0.01	<1	<10	<2
CH-4	2	7.75	488	7.1	<5	1.95	2	34	159	2065	5.81	1.86	1.49	479	<2	3.26	54	704	15	209	0.33	103	<10	213

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V3384RR

Date : Oct-29-08

WHY Resources

Attention: Mike Godin

Project: Record Ridge South/08

Sample type: Rock

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
46001	<1	0.07	11	<0.5	<5	0.66	4	101	1644	2	5.14	0.02	23.12	2102	<2	0.03	2076	16	36	49	<0.01	6	<10	63
46002	<1	0.06	12	<0.5	<5	0.57	5	112	775	2	5.91	0.02	25.84	1154	<2	0.02	2154	<10	22	75	<0.01	7	<10	43
46003	<1	0.06	11	<0.5	<5	0.18	6	109	938	2	6.77	0.01	24.97	871	<2	0.02	2164	<10	10	23	<0.01	9	<10	33
46004	<1	0.07	<10	<0.5	<5	0.28	5	111	1164	2	5.86	0.01	24.10	972	<2	0.02	2206	<10	10	26	<0.01	10	<10	36
46005	<1	0.12	<10	<0.5	<5	0.55	4	106	1318	3	5.38	0.01	24.18	1227	<2	0.02	1968	<10	11	39	<0.01	15	<10	42
46006	<1	0.09	11	<0.5	<5	0.45	5	121	1700	3	5.37	0.01	25.77	1265	<2	0.02	2108	<10	16	37	<0.01	11	<10	47
46007	<1	0.08	<10	<0.5	<5	0.12	5	119	908	2	6.00	0.01	27.37	897	<2	0.02	2238	<10	9	9	<0.01	15	<10	28
46008	<1	0.11	<10	<0.5	<5	0.21	5	117	1057	2	6.03	0.01	26.29	885	<2	0.03	2291	<10	10	11	<0.01	17	<10	29
46009	<1	0.14	50	<0.5	<5	0.23	5	110	1343	2	6.01	0.01	26.00	877	<2	0.03	2205	<10	10	15	<0.01	17	<10	35
46010	<1	0.12	12	<0.5	<5	0.30	5	109	1351	2	5.84	0.01	25.60	905	<2	0.04	2153	<10	9	20	<0.01	14	<10	34
46011	<1	0.13	<10	<0.5	<5	0.38	5	112	1301	14	5.46	0.01	24.08	869	<2	0.03	2200	<10	12	25	<0.01	19	<10	30
46012	<1	0.13	11	<0.5	<5	0.49	5	113	1725	1	5.87	0.01	24.67	904	<2	0.03	2080	<10	8	32	<0.01	17	<10	39
46013	<1	0.11	<10	<0.5	<5	1.06	5	119	2062	<1	6.27	0.01	24.74	1004	<2	0.02	2140	<10	8	39	<0.01	16	<10	43
46014	<1	0.14	<10	<0.5	<5	1.26	5	114	1879	2	5.90	0.01	24.39	951	<2	0.03	2194	<10	9	83	<0.01	18	<10	43
46015	<1	0.13	<10	<0.5	<5	1.37	5	112	1697	<1	6.24	0.01	26.15	858	<2	0.03	2049	<10	7	47	<0.01	19	<10	41
46016	<1	0.11	10	<0.5	<5	0.73	5	114	1528	2	6.17	0.01	24.27	885	<2	0.02	2129	<10	5	22	<0.01	18	<10	37
46017	<1	0.10	<10	<0.5	<5	0.36	5	109	1253	<1	5.85	0.01	24.71	929	<2	0.02	2184	<10	5	8	<0.01	16	<10	34
46018	<1	0.11	60	<0.5	<5	0.91	5	106	1085	1	5.47	0.08	23.60	911	<2	0.02	1962	<10	10	34	<0.01	18	<10	32
46019	<1	1.56	179	0.6	<5	1.65	5	109	1386	13	6.10	0.22	21.42	1185	<2	0.16	1777	656	27	138	0.13	60	<10	73
46020	<1	6.50	1483	4.5	<5	5.58	4	61	573	36	7.78	2.91	9.82	1946	<2	0.90	189	3346	164	679	0.65	215	<10	169
46021	<1	2.34	29	<0.5	<5	0.58	5	93	1249	42	6.13	0.16	21.12	1075	<2	0.05	1602	350	30	19	0.13	79	<10	56
46022	<1	2.24	579	1.5	<5	2.89	4	94	1050	19	5.98	1.09	17.76	1270	<2	0.35	1319	1307	51	279	0.24	80	<10	78
46023	<1	0.09	<10	<0.5	<5	0.57	5	115	1242	2	5.70	0.02	25.82	951	<2	0.02	1841	<10	11	22	<0.01	13	<10	57
46024	<1	0.08	10	<0.5	<5	1.36	5	116	1348	8	5.96	0.02	25.13	951	2	0.02	1764	64	15	69	<0.01	15	<10	63
46025	<1	0.08	<10	<0.5	<5	0.84	5	119	1368	9	5.68	0.01	25.55	989	<2	0.02	1917	26	21	72	<0.01	12	<10	67
46026	<1	0.08	10	<0.5	<5	0.39	5	130	1266	2	6.18	0.01	26.76	976	<2	0.02	2136	<10	13	32	<0.01	13	<10	59
46027	<1	0.08	<10	<0.5	<5	0.96	6	123	1435	5	6.63	0.02	26.20	1013	<2	0.02	1986	<10	9	35	<0.01	15	<10	61
46028	<1	0.08	<10	<0.5	<5	0.33	5	111	1397	12	5.65	0.04	25.61	925	<2	0.03	1818	<10	13	38	<0.01	13	<10	62
46029	<1	0.09	<10	<0.5	<5	0.53	5	108	1516	9	5.80	0.02	25.00	996	<2	0.02	1774	<10	14	22	<0.01	15	<10	62
46030	<1	0.11	<10	<0.5	<5	0.60	5	109	2459	9	6.02	0.01	24.56	954	2	0.03	1718	23	8	34	<0.01	16	<10	73

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V3384RR

Date : Oct-29-08

WHY Resources

Attention: Mike Godin

Project: Record Ridge South/08

Sample type: Rock

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
46031	<1	0.08	<10	<0.5	<5	1.76	5	109	1713	6	5.88	0.01	25.07	1055	2	0.02	1835	25	8	99	<0.01	14	<10	69
46032	<1	0.09	10	<0.5	<5	1.39	5	117	1828	6	5.75	0.02	24.26	1001	2	0.03	1873	19	7	67	<0.01	15	<10	65
46033	<1	0.10	<10	<0.5	<5	0.69	5	121	1263	1	6.07	0.02	26.02	899	2	0.03	1966	<10	10	48	<0.01	15	<10	49
46034	<1	0.11	<10	<0.5	<5	0.25	5	111	1299	2	6.33	0.02	27.43	927	<2	0.03	1909	<10	8	4	0.01	16	<10	51
46035	<1	0.09	<10	<0.5	<5	0.32	6	129	1914	2	6.76	0.01	27.13	1049	<2	0.02	2125	<10	6	5	<0.01	14	<10	57
46036	<1	0.08	<10	<0.5	<5	0.17	6	118	1079	1	6.15	0.01	27.90	967	<2	0.02	1907	<10	10	3	<0.01	12	<10	48
46037	<1	0.12	<10	<0.5	<5	0.05	6	117	1437	6	6.16	0.01	27.57	928	<2	0.03	1878	<10	6	1	0.01	15	<10	50
46038	<1	0.09	<10	<0.5	<5	0.13	5	115	1432	<1	6.07	0.01	27.58	952	<2	0.02	1886	<10	8	3	<0.01	12	<10	49
46039	<1	0.08	<10	<0.5	<5	0.11	6	122	1461	<1	6.59	0.01	27.89	962	<2	0.02	1994	<10	9	3	<0.01	11	<10	49
46040	<1	0.06	<10	<0.5	<5	0.34	5	137	1045	<1	6.15	0.01	29.75	1049	<2	0.02	2242	<10	7	9	<0.01	10	<10	47
46041	<1	0.05	<10	<0.5	<5	0.47	6	132	872	<1	6.36	0.01	30.89	1105	<2	0.02	2321	<10	8	14	<0.01	10	<10	47
46042	<1	0.09	<10	<0.5	<5	0.25	7	140	1631	4	7.65	0.02	31.59	1094	<2	0.02	2308	<10	9	14	<0.01	12	<10	55
46043	<1	0.08	<10	<0.5	<5	0.22	6	126	1454	4	6.62	0.02	28.73	993	<2	0.02	2116	<10	8	8	<0.01	12	<10	51
46044	<1	0.08	<10	<0.5	<5	0.35	5	124	1615	4	5.66	0.01	27.89	997	<2	0.02	2090	<10	6	14	<0.01	10	<10	53
46045	<1	0.11	11	<0.5	<5	0.36	5	110	1565	2	6.62	0.01	25.53	959	<2	0.02	2137	13	8	13	<0.01	10	<10	43
46046	<1	0.16	10	<0.5	<5	0.37	5	117	2633	1	6.96	0.01	25.63	985	<2	0.02	2050	<10	4	12	<0.01	10	<10	55
46047	<1	0.14	<10	<0.5	<5	0.35	5	114	2789	3	6.50	0.01	26.98	1022	<2	0.02	2050	<10	18	11	<0.01	9	<10	64
46048	<1	0.15	<10	<0.5	<5	0.48	4	116	2924	2	6.14	0.01	28.26	1174	<2	0.02	2211	<10	10	16	<0.01	8	<10	66
46049	<1	0.07	10	<0.5	<5	0.40	5	115	1397	2	6.38	0.01	27.23	1064	<2	0.02	2246	<10	13	9	<0.01	9	<10	42
46050	<1	0.06	<10	<0.5	<5	0.28	5	113	812	5	6.05	0.01	28.02	976	<2	0.03	2240	<10	4	7	<0.01	7	<10	33
46051	<1	0.10	<10	<0.5	<5	0.32	4	105	1570	2	5.47	0.01	24.82	856	<2	0.03	2052	<10	5	3	<0.01	10	<10	45
46052	<1	1.04	82	<0.5	<5	1.88	4	101	1052	12	6.00	0.01	22.07	977	<2	0.03	1834	111	8	21	0.06	38	<10	46
46053	<1	6.71	1685	1.3	<5	2.19	4	73	492	62	8.23	0.62	16.29	1534	<2	0.65	738	733	40	405	0.42	247	<10	94
46054	<1	0.12	11	<0.5	<5	0.29	5	112	1570	5	6.38	0.01	24.84	881	<2	0.02	2215	10	8	8	<0.01	12	<10	44
46055	<1	6.37	1267	1.2	<5	3.48	4	73	659	53	8.19	0.19	17.65	1584	<2	0.37	856	702	36	758	0.40	242	<10	87
46056	<1	0.11	12	<0.5	<5	1.02	5	114	1298	12	5.91	0.01	23.59	911	<2	0.03	2073	<10	9	14	<0.01	10	<10	42
46057	<1	0.15	14	<0.5	<5	0.88	4	104	1270	1	5.69	0.01	25.39	878	<2	0.02	1930	10	10	27	<0.01	12	<10	42
46058	<1	0.77	27	<0.5	<5	2.09	5	118	1885	8	6.26	0.03	19.18	1171	<2	0.05	2209	83	8	65	0.02	21	<10	92
46059	<1	9.60	1761	1.6	<5	0.95	<1	26	43	7	5.49	2.83	6.91	1200	<2	3.91	57	1185	47	548	0.33	121	<10	120
46060	<1	6.49	67	1.0	<5	1.15	4	82	1051	258	7.65	0.41	17.50	1612	<2	0.31	1002	677	33	173	0.37	224	<10	94

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

WHY Resources

Attention: Mike Godin

Project: Record Ridge South/08

Sample type: Rock

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V3384RR

Date : Oct-29-08

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
46061	<1	0.22	14	<0.5	<5	0.18	5	111	2289	2	6.69	0.02	24.06	843	<2	0.04	2134	<10	14	9	0.01	15	<10	48
46062	<1	0.17	10	<0.5	<5	0.36	5	110	1699	2	6.08	0.01	24.98	852	<2	0.03	2240	<10	16	11	0.01	13	<10	42
46063	<1	0.14	<10	<0.5	<5	0.18	5	116	2797	3	6.10	0.01	26.63	1028	<2	0.03	2191	<10	14	3	<0.01	10	<10	56
46064	<1	0.13	<10	<0.5	<5	0.13	5	120	1798	5	6.37	0.01	28.38	966	<2	0.03	2178	<10	11	3	<0.01	11	<10	47
46065	<1	0.14	<10	<0.5	<5	0.10	4	112	1990	1	5.61	0.01	26.09	856	<2	0.03	1991	<10	11	4	<0.01	10	<10	49
46066	<1	0.16	<10	<0.5	<5	0.14	5	110	1754	6	6.07	0.01	25.59	836	<2	0.03	2236	<10	12	6	<0.01	12	<10	46
46067	<1	0.13	<10	<0.5	8	0.49	3	116	1757	7	5.69	<0.01	26.29	836	<2	0.02	2440	<10	6	13	<0.01	12	<10	36
46068	<1	0.10	<10	<0.5	8	0.18	4	118	1379	<1	6.13	<0.01	26.85	1003	<2	0.01	2530	<10	10	2	<0.01	13	<10	38
46069	<1	0.11	<10	<0.5	6	0.22	3	113	1543	3	5.54	<0.01	26.10	884	<2	0.01	2400	<10	13	3	<0.01	13	<10	47
46070	<1	0.08	<10	<0.5	8	0.21	5	136	1394	22	6.92	<0.01	31.10	987	<2	0.01	2994	<10	8	5	<0.01	11	<10	33
46071	<1	0.09	<10	<0.5	8	0.22	4	132	1910	11	6.94	0.01	29.85	1092	<2	0.01	2751	<10	7	3	<0.01	11	<10	31
46072	<1	0.07	<10	<0.5	8	0.47	5	139	1200	9	7.29	<0.01	31.18	1048	<2	0.01	2972	<10	10	9	<0.01	10	<10	24
46073	<1	0.07	<10	<0.5	7	0.29	5	133	1208	16	6.83	<0.01	30.80	1059	<2	0.01	2691	<10	9	7	<0.01	10	<10	22
46074	<1	0.08	<10	<0.5	7	0.10	5	128	984	7	7.09	<0.01	29.96	949	<2	0.01	2711	<10	13	3	<0.01	12	<10	18
46075	<1	0.11	<10	<0.5	7	0.53	4	130	1254	7	6.73	<0.01	29.84	1098	<2	0.01	2639	<10	7	27	<0.01	12	<10	24
46076	<1	0.08	<10	<0.5	8	0.33	5	137	1482	3	7.41	<0.01	29.49	994	<2	0.01	2729	<10	5	11	<0.01	11	<10	25
46077	<1	0.08	<10	<0.5	8	0.51	4	139	1386	10	7.14	<0.01	29.91	1039	<2	0.01	2780	<10	5	12	<0.01	11	<10	27
46078	<1	0.09	<10	<0.5	7	0.22	4	126	1096	3	6.91	<0.01	29.53	1077	<2	0.01	2620	<10	6	5	<0.01	13	<10	27
46079	<1	0.10	<10	<0.5	6	0.65	4	141	1175	8	6.44	<0.01	30.66	1134	<2	0.01	2841	<10	6	8	<0.01	13	<10	35
46080	<1	0.11	35	<0.5	6	0.17	4	120	1187	71	6.21	<0.01	29.66	932	<2	0.01	2636	<10	10	12	<0.01	12	<10	35
46081	<1	0.11	<10	<0.5	8	0.61	4	128	1736	3	6.39	<0.01	29.54	1006	<2	0.01	2524	<10	6	9	<0.01	11	<10	38
46082	<1	0.09	<10	<0.5	7	0.09	4	126	1449	6	6.88	<0.01	29.94	945	<2	0.01	2814	<10	8	3	<0.01	10	<10	31
46083	<1	0.11	<10	<0.5	9	0.14	6	140	2201	1	9.69	<0.01	28.83	1023	<2	0.01	3167	<10	6	10	<0.01	13	<10	36
46084	<1	0.12	<10	<0.5	9	0.16	4	131	2628	1	6.97	0.01	29.63	1006	<2	0.02	2710	<10	9	4	<0.01	10	<10	42
46085	<1	0.10	<10	<0.5	7	0.17	4	129	1634	6	6.89	<0.01	29.97	976	<2	0.02	2628	<10	9	2	<0.01	10	<10	28
46086	<1	0.13	<10	<0.5	7	0.06	4	120	1607	2	6.53	<0.01	29.51	904	<2	0.02	2636	<10	5	1	<0.01	15	<10	25
46087	<1	0.09	<10	<0.5	7	0.13	4	126	1061	2	6.47	<0.01	30.11	915	<2	0.02	2790	<10	11	3	<0.01	12	<10	19
46088	<1	0.12	<10	<0.5	8	0.09	3	118	2496	2	7.06	<0.01	28.34	966	<2	0.02	1993	<10	6	4	<0.01	19	<10	42
46089	<1	0.13	14	<0.5	<5	0.07	6	115	1327	<1	6.90	0.02	26.90	914	2	0.02	2242	<10	2	7	<0.01	16	<10	36
46090	<1	0.12	14	<0.5	<5	0.24	6	121	1442	1	6.62	0.02	27.43	972	<2	0.02	2380	13	21	11	<0.01	14	<10	38

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

WHY Resources

Attention: Mike Godin

Project: Record Ridge South/08

Sample type: Rock

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V3384RR

Date : Oct-29-08

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
46091	<1	0.11	<10	<0.5	<5	0.30	5	113	1255	<1	5.94	0.01	25.54	950	<2	0.02	2205	<10	10	17	<0.01	13	<10	41
46092	<1	0.10	<10	<0.5	<5	0.10	7	121	1669	<1	8.16	0.01	25.07	966	<2	0.02	2332	<10	<2	2	<0.01	15	<10	42
46093	<1	0.32	85	<0.5	<5	0.30	5	116	1953	<1	6.18	0.20	24.41	1099	<2	0.05	2100	86	4	25	0.03	19	<10	56
46094	<1	0.10	16	<0.5	<5	0.19	7	135	2119	<1	7.90	0.03	26.12	1131	<2	0.02	2181	<10	7	10	<0.01	14	<10	72
46095	<1	7.08	1823	5.0	<5	5.73	4	63	515	29	7.67	3.71	7.72	1458	<2	1.43	301	3476	56	746	0.63	186	<10	107
46096	<1	0.23	14	<0.5	<5	0.75	22	129	2900	8	7.60	0.02	25.87	1467	<2	0.02	2272	14	1644	31	<0.01	16	39	2668
46097	<1	0.18	15	<0.5	<5	0.41	7	130	2344	4	7.21	0.02	26.73	1154	<2	0.02	2299	57	17	24	0.01	16	<10	117
46098	<1	0.13	13	<0.5	<5	1.22	5	106	1724	4	6.49	0.01	24.27	1021	<2	0.02	2051	62	3	59	<0.01	19	<10	67
46099	<1	0.16	<10	<0.5	<5	0.47	5	108	1249	2	6.03	0.01	24.33	871	<2	0.02	2125	13	<2	11	<0.01	20	<10	45
46100	<1	0.16	<10	<0.5	<5	0.19	5	109	1248	2	6.22	0.01	25.03	867	2	0.02	2033	<10	<2	5	<0.01	22	<10	37
Duplicates:																								
46001	<1	0.08	13	<0.5	<5	0.72	5	106	1672	3	5.32	0.02	25.16	2213	<2	0.03	2163	15	37	51	<0.01	6	<10	63
46010	<1	0.12	<10	<0.5	<5	0.29	5	111	1536	2	5.60	0.01	25.19	900	<2	0.03	2209	<10	11	20	<0.01	15	<10	35
46020	<1	6.92	1521	4.4	<5	5.68	4	65	581	36	7.87	2.92	10.02	1962	<2	0.94	195	3576	163	694	0.67	221	<10	178
46023	<1	0.10	<10	<0.5	<5	0.57	5	120	1428	4	5.64	0.01	25.70	946	<2	0.02	1805	<10	7	21	<0.01	12	<10	56
46032	<1	0.13	11	<0.5	<5	1.42	5	118	1748	6	5.72	0.04	24.64	1012	2	0.09	1846	<10	18	69	<0.01	14	<10	64
46042	<1	0.09	<10	<0.5	<5	0.24	7	135	1578	4	7.36	0.02	29.64	1053	<2	0.02	2220	12	18	13	<0.01	12	<10	53
46045	<1	0.11	10	<0.5	<5	0.35	5	112	1554	3	6.31	0.01	25.17	957	<2	0.02	2205	<10	13	13	<0.01	10	<10	40
46054	<1	0.13	<10	<0.5	<5	0.27	5	109	1565	3	6.07	0.01	23.77	853	<2	0.02	2171	<10	11	8	<0.01	11	<10	42
46064	<1	0.14	<10	<0.5	<5	0.12	5	115	1875	1	6.22	0.01	27.54	942	<2	0.03	2217	<10	11	3	<0.01	10	<10	49
46067	<1	0.12	<10	<0.5	6	0.50	3	114	1453	1	5.81	<0.01	26.71	826	<2	0.02	2441	<10	5	13	<0.01	12	<10	36
46076	<1	0.08	<10	<0.5	8	0.35	5	144	1560	4	8.00	<0.01	30.96	1028	<2	0.01	2836	<10	5	10	<0.01	12	<10	28
46086	<1	0.12	<10	<0.5	7	0.06	4	118	1408	<1	6.48	<0.01	28.94	881	<2	0.02	2591	<10	7	1	<0.01	14	<10	22
46089	<1	0.13	15	<0.5	<5	0.08	6	118	1148	1	6.99	0.02	27.68	936	<2	0.02	2307	<10	2	6	<0.01	16	<10	34
46098	<1	0.12	14	<0.5	<5	1.20	5	108	1738	2	6.36	<0.01	23.88	1037	<2	0.01	2083	63	4	60	<0.01	20	<10	67
Standards:																								
Blank	<1	<0.01	<10	<0.5	<5	<0.01	<1	2	4	<1	0.01	<0.01	0.02	<5	<2	0.01	2	<10	<2	<1	<0.01	<1	<10	<2
CH-4	2	7.59	512	1.8	<5	2.34	3	34	139	2048	6.70	2.10	1.57	492	2	3.78	56	791	11	194	0.33	99	10	224

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V3438RR

Date : Dec-05-08

WHY Resources

Attention: Michael Godin

Project: Record Ridge South

Sample type: Core

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
46101	2	0.12	11	<0.5	<5	0.40	4	104	941	6	5.71	0.01	25.17	884	2	0.02	1951	<10	<2	18	<0.01	12	<10	51
46102	<1	0.12	<10	<0.5	<5	0.18	4	120	1462	4	6.14	0.01	28.25	1029	<2	0.02	2248	<10	<2	8	<0.01	10	<10	61
46103	<1	0.11	<10	<0.5	<5	0.33	5	124	1146	31	6.58	0.01	29.67	1115	<2	0.02	2440	<10	9	11	<0.01	12	<10	81
46104	<1	0.11	<10	<0.5	<5	0.24	5	125	1580	3	6.65	0.01	30.61	992	<2	0.01	2310	<10	<2	6	<0.01	10	<10	48
46105	<1	0.11	<10	<0.5	<5	0.16	5	122	1194	3	6.27	0.01	29.50	901	<2	0.02	2278	<10	<2	5	<0.01	13	<10	35
46106	<1	0.15	<10	<0.5	<5	0.11	4	112	1456	2	5.63	0.01	28.10	823	<2	0.02	2008	<10	<2	4	<0.01	14	<10	34
46107	<1	0.13	<10	<0.5	<5	0.21	4	116	1735	2	6.04	<0.01	27.24	897	<2	0.02	1906	<10	<2	6	<0.01	10	<10	41
46108	<1	0.09	<10	<0.5	<5	0.20	4	109	1307	3	6.09	0.01	26.63	753	<2	0.02	2058	<10	<2	7	<0.01	9	<10	33
46109	<1	0.12	11	<0.5	<5	0.39	4	104	1073	5	5.63	0.01	24.81	1076	<2	0.02	1868	26	<2	27	<0.01	13	<10	45
46110	<1	0.11	<10	<0.5	<5	0.36	4	112	1690	3	5.45	0.01	25.37	1278	<2	0.02	1971	23	<2	19	<0.01	11	<10	63
46111	<1	0.12	<10	<0.5	<5	0.19	5	123	1676	3	6.62	0.01	30.14	1070	<2	0.02	2318	<10	3	8	<0.01	11	<10	59
46112	<1	0.07	11	<0.5	<5	0.54	5	121	1217	5	6.71	0.01	26.74	1050	3	0.02	2188	<10	23	48	<0.01	8	<10	58
46113	<1	0.10	11	<0.5	<5	0.13	4	116	1447	2	5.94	<0.01	28.35	862	<2	0.02	2121	<10	<2	13	<0.01	7	<10	45
46114	<1	0.08	<10	<0.5	<5	0.13	4	114	1488	3	5.37	<0.01	28.10	802	<2	0.01	2252	<10	<2	9	<0.01	4	<10	43
46115	<1	0.06	<10	<0.5	<5	0.18	4	111	1363	2	5.70	<0.01	27.78	901	<2	0.01	2118	<10	<2	14	<0.01	5	<10	40
46116	<1	0.10	<10	<0.5	<5	0.17	5	123	1868	2	6.62	<0.01	29.18	984	<2	0.02	2351	<10	<2	13	<0.01	5	<10	54
46117	<1	0.06	<10	<0.5	<5	0.34	4	116	934	2	5.00	<0.01	28.12	976	<2	0.01	2174	<10	<2	23	<0.01	4	<10	37
46118	<1	1.20	20	<0.5	<5	1.24	4	117	1338	9	5.92	0.07	25.54	1114	<2	0.02	2129	155	<2	34	0.06	41	<10	62
46119	<1	0.65	12	<0.5	<5	0.81	4	114	1956	5	5.46	0.03	25.00	901	<2	0.02	2034	67	<2	24	0.02	22	<10	55
46120	<1	3.60	42	<0.5	<5	0.99	4	92	1163	65	6.92	0.17	24.25	1053	<2	0.06	1239	468	8	19	0.17	101	<10	82
46121	<1	0.10	<10	<0.5	<5	0.18	4	130	1452	3	6.26	<0.01	27.79	898	<2	0.02	2479	30	<2	7	<0.01	7	<10	54
46122	<1	0.12	<10	<0.5	<5	0.27	4	133	1362	2	5.59	0.01	29.30	983	<2	0.01	2328	<10	<2	12	<0.01	6	<10	49
46123	<1	0.09	<10	<0.5	6	0.28	3	126	1441	3	5.65	0.01	27.88	965	<2	0.01	2360	13	13	12	<0.01	7	<10	44
46124	<1	0.11	<10	<0.5	7	0.59	3	122	1876	1	5.82	<0.01	25.74	953	<2	0.01	2069	29	14	13	<0.01	8	<10	52
46125	<1	2.77	18	<0.5	<5	0.69	3	100	1000	13	6.35	0.10	23.62	1023	<2	0.02	1433	306	25	15	0.13	82	<10	47
46126	<1	0.07	<10	<0.5	8	0.43	3	112	2030	1	5.62	<0.01	26.24	993	<2	0.01	2201	<10	16	6	<0.01	6	<10	41
46127	<1	0.11	<10	<0.5	8	1.81	3	122	2241	1	5.64	<0.01	27.72	1082	<2	0.01	2207	<10	10	33	<0.01	7	<10	58
46128	<1	2.40	13	<0.5	<5	0.94	3	103	1258	8	6.68	0.03	24.58	1077	<2	0.02	1755	273	21	22	0.11	79	<10	49
46129	<1	0.13	<10	<0.5	7	0.42	4	117	1191	1	6.38	<0.01	25.22	817	<2	0.02	2307	<10	6	9	<0.01	14	<10	21
46130	<1	0.13	<10	<0.5	10	0.51	4	117	1647	<1	6.01	<0.01	26.65	930	<2	0.01	2206	<10	9	8	<0.01	11	<10	31

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

WHY Resources

Attention: Michael Godin

Project: Record Ridge South

Sample type: Core

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V3438RR

Date : Dec-05-08

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
46131	<1	0.13	<10	<0.5	10	0.23	4	122	2302	1	6.45	<0.01	28.09	981	<2	0.02	2198	<10	9	7	<0.01	12	<10	44
46132	<1	0.11	<10	<0.5	9	0.08	4	115	1662	<1	6.25	<0.01	26.81	886	<2	0.01	2209	<10	8	6	<0.01	13	<10	32
46133	<1	0.11	<10	<0.5	9	0.08	3	122	2651	<1	6.01	<0.01	27.58	1044	<2	0.01	2260	<10	4	3	<0.01	7	<10	46
46134	<1	0.22	<10	<0.5	8	0.41	4	121	1777	5	6.29	0.01	27.00	951	<2	0.02	2311	<10	8	6	0.01	14	<10	31
46135	<1	0.33	<10	<0.5	7	0.44	4	115	1511	5	6.14	0.01	26.62	881	<2	0.02	2257	<10	6	6	0.01	19	<10	22
46136	<1	0.30	<10	<0.5	8	0.52	4	117	1929	7	6.45	0.01	26.65	896	<2	0.02	2239	<10	11	6	0.01	17	<10	27
46137	<1	0.51	11	<0.5	6	0.47	4	110	1378	5	5.54	0.04	26.87	813	<2	0.02	2126	48	9	6	0.02	19	<10	27
46138	<1	0.32	<10	<0.5	8	0.53	4	120	1655	4	6.57	0.01	27.76	925	<2	0.02	2284	<10	8	7	0.01	20	<10	25
46139	<1	0.56	<10	<0.5	7	0.75	4	110	1332	2	5.74	0.02	25.14	896	<2	0.01	2048	60	9	43	0.03	22	<10	33
46140	<1	6.92	1998	4.4	<5	4.50	6	70	373	11	8.45	1.93	8.62	1741	<2	1.26	345	5193	343	1250	0.83	177	<10	263
46141	<1	0.34	62	<0.5	5	1.40	4	119	1437	1	6.09	0.07	25.18	968	<2	0.02	2150	123	14	62	0.03	19	<10	39
46142	<1	0.23	20	<0.5	7	2.15	4	118	1609	1	5.97	0.02	25.63	964	<2	0.03	2143	34	13	87	0.01	18	<10	37
46143	<1	0.23	41	<0.5	6	1.98	3	105	1832	7	5.33	0.01	23.15	965	<2	0.02	2048	<10	16	109	0.01	14	<10	60
46144	<1	5.95	1670	2.6	<5	2.85	4	80	667	5	7.41	1.86	12.56	1728	<2	1.06	841	2997	160	721	0.50	118	<10	182
46145	<1	0.14	15	<0.5	10	1.85	5	118	2107	2	6.82	0.01	24.42	964	<2	0.03	1993	<10	9	48	<0.01	14	<10	50
46146	<1	0.15	17	<0.5	9	2.08	4	114	1951	4	5.63	0.02	25.40	1075	<2	0.02	1862	39	44	131	<0.01	12	<10	51
46147	<1	0.14	11	<0.5	11	0.80	4	119	1960	1	6.39	<0.01	26.76	866	<2	0.04	2061	<10	9	76	<0.01	12	<10	37
46148	<1	0.67	10	<0.5	6	1.09	4	127	1665	1	6.40	0.01	27.00	1046	<2	0.02	2023	77	6	53	0.04	30	<10	30
46149	<1	0.31	<10	<0.5	10	1.25	4	124	1913	<1	6.59	0.01	27.97	996	<2	0.02	2118	<10	3	30	0.01	20	<10	27
46150	<1	0.53	11	<0.5	9	0.89	5	139	2026	1	7.23	0.02	28.76	965	<2	0.03	2201	56	4	63	0.03	21	<10	25
46151	<1	0.34	<10	<0.5	8	1.26	4	128	1767	10	6.68	0.01	29.28	1022	<2	0.02	2251	16	2	27	0.01	18	<10	23
46152	<1	0.37	60	<0.5	9	0.08	4	131	1401	3	6.27	0.14	28.07	977	<2	0.13	2125	39	7	37	0.01	14	<10	23
46153	<1	0.11	11	<0.5	10	0.05	5	149	2487	2	8.11	<0.01	28.11	987	<2	0.01	2322	<10	6	4	<0.01	12	<10	44
46154	<1	0.08	<10	<0.5	8	0.10	4	134	1062	4	6.22	<0.01	28.73	931	<2	0.01	2178	<10	3	6	<0.01	10	<10	20
46155	<1	0.12	<10	<0.5	9	0.09	4	133	1350	5	6.07	<0.01	29.10	1064	<2	0.02	2058	<10	6	10	<0.01	11	<10	28
46156	<1	0.11	<10	<0.5	9	0.11	4	134	1166	5	6.53	<0.01	28.63	1075	<2	0.02	2165	<10	5	9	<0.01	12	<10	26
46157	<1	0.10	<10	<0.5	9	0.25	4	140	1507	2	6.24	<0.01	28.72	1217	<2	0.01	2116	<10	3	14	<0.01	10	<10	32
46158	<1	0.12	<10	<0.5	8	0.57	4	125	1406	3	6.17	<0.01	27.18	1061	<2	0.02	2068	<10	6	18	<0.01	12	<10	30
46159	<1	0.08	15	<0.5	7	4.97	2	87	978	5	4.13	<0.01	23.71	1260	<2	0.01	1200	34	3	123	<0.01	10	<10	28
46160	<1	0.10	<10	<0.5	8	0.77	4	127	2147	7	6.39	<0.01	28.19	1116	<2	0.01	2240	<10	3	13	<0.01	10	<10	43

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V3438RR

Date : Dec-05-08

WHY Resources

Attention: Michael Godin

Project: Record Ridge South

Sample type: Core

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
46161	<1	0.10	<10	<0.5	9	1.21	4	127	1700	5	6.80	<0.01	28.10	1058	<2	0.01	2195	<10	5	18	<0.01	12	<10	35
46162	<1	1.17	10	<0.5	6	0.77	4	132	1699	11	7.42	0.01	26.06	1105	<2	0.02	2055	143	10	23	0.06	46	<10	37
46163	<1	5.51	20	0.5	<5	2.20	5	99	942	2	8.20	0.14	20.77	1679	<2	0.29	1135	801	31	500	0.31	168	<10	58
46164	<1	0.17	<10	<0.5	10	0.22	4	126	2445	1	7.14	<0.01	27.33	795	<2	0.02	2091	<10	7	13	0.01	12	<10	42
46165	<1	0.14	<10	<0.5	10	0.37	4	124	2032	4	6.30	<0.01	28.50	985	<2	0.02	2117	<10	4	14	<0.01	11	<10	40
46166	<1	0.13	<10	<0.5	9	0.71	4	122	1494	8	5.83	0.01	27.30	1161	<2	0.02	2045	<10	7	15	<0.01	9	<10	38
46167	<1	7.29	1782	4.1	<5	4.61	2	35	224	27	6.02	3.65	3.71	1049	3	2.49	52	3020	36	1060	0.59	166	<10	98
46168	<1	8.05	1812	4.3	<5	5.19	2	42	264	24	6.43	3.67	4.28	1102	2	2.48	77	3436	40	1084	0.65	175	<10	98
46169	<1	0.10	13	<0.5	<5	0.25	6	109	1185	7	6.65	0.02	28.01	1052	<2	0.03	1983	<10	6	13	<0.01	12	<10	74
46170	<1	0.08	<10	<0.5	<5	0.05	6	107	1133	4	6.62	0.01	28.19	960	<2	0.02	1926	<10	<2	3	<0.01	10	<10	64
46171	<1	0.10	<10	<0.5	<5	0.16	6	104	1099	6	6.43	0.01	28.33	944	<2	0.02	1854	<10	<2	6	<0.01	13	<10	58
46172	<1	0.10	<10	<0.5	<5	0.22	5	105	973	16	6.00	0.01	27.68	917	<2	0.02	1866	<10	<2	3	<0.01	13	<10	49
46173	<1	0.09	<10	<0.5	<5	0.18	6	107	954	15	6.30	0.01	28.10	912	<2	0.03	2061	<10	<2	5	<0.01	13	<10	51
46174	<1	0.10	<10	<0.5	<5	0.21	5	105	1273	7	6.26	<0.01	27.90	870	<2	0.02	2031	<10	<2	6	<0.01	13	<10	48
46175	<1	0.13	<10	<0.5	<5	0.17	5	105	1324	8	6.15	0.01	29.27	865	<2	0.04	2099	<10	<2	3	<0.01	14	<10	51
46176	<1	0.11	<10	<0.5	<5	0.27	5	111	1502	4	6.78	<0.01	29.68	933	<2	0.02	2004	<10	<2	7	<0.01	11	<10	52
46177	<1	0.05	<10	<0.5	<5	0.18	6	109	940	6	6.78	<0.01	28.86	875	<2	0.02	2207	<10	<2	7	<0.01	8	<10	50
46178	<1	0.06	<10	<0.5	<5	0.33	6	109	1639	9	6.85	<0.01	28.72	951	<2	0.02	2010	<10	<2	12	<0.01	7	<10	62
46179	<1	0.09	<10	<0.5	<5	0.66	5	101	1139	7	6.09	0.01	27.21	1110	<2	0.02	1868	<10	2	28	<0.01	11	<10	55
46180	<1	0.10	<10	<0.5	<5	0.40	5	106	1459	19	6.29	<0.01	28.40	889	<2	0.02	1968	<10	<2	5	<0.01	12	<10	49
46181	<1	0.08	<10	<0.5	<5	0.32	5	106	1394	117	5.87	<0.01	28.16	847	<2	0.02	1929	<10	<2	6	<0.01	11	<10	53
46182	<1	0.09	<10	<0.5	<5	0.32	6	102	1342	39	6.80	<0.01	27.84	933	<2	0.02	1942	<10	<2	11	<0.01	12	<10	52
46183	<1	0.07	<10	<0.5	<5	0.44	5	104	1197	37	6.20	<0.01	27.47	1012	<2	0.02	1973	<10	<2	22	<0.01	11	<10	56
46184	<1	0.09	<10	<0.5	<5	0.15	5	102	1433	54	5.93	<0.01	27.71	843	<2	0.02	1864	<10	<2	3	<0.01	13	<10	53
46185	<1	0.10	<10	<0.5	<5	0.41	5	105	1984	32	6.36	<0.01	26.72	1064	<2	0.02	2007	<10	<2	13	<0.01	13	<10	65
46186	<1	0.08	12	<0.5	<5	1.61	6	97	1583	14	6.50	<0.01	23.88	1277	<2	0.02	1730	<10	9	81	<0.01	12	<10	73
46187	<1	0.09	<10	<0.5	<5	0.27	5	105	2130	13	6.12	<0.01	26.62	825	<2	0.02	1981	<10	<2	10	<0.01	11	<10	65
46188	<1	0.10	<10	<0.5	<5	0.47	5	101	1449	11	5.75	<0.01	26.38	811	<2	0.02	1855	<10	<2	27	<0.01	14	<10	55
46189	<1	0.11	<10	<0.5	<5	0.18	5	111	1610	9	6.38	0.01	25.69	939	<2	0.02	2046	<10	<2	3	<0.01	15	<10	44
46190	<1	0.11	<10	<0.5	<5	0.12	5	111	1300	6	6.32	0.01	25.73	910	<2	0.02	2069	<10	<2	2	<0.01	16	<10	38

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

WHY Resources

Attention: Michael Godin

Project: Record Ridge South

Sample type: Core

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V3438RR

Date : Dec-05-08

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
46191	<1	0.09	<10	<0.5	<5	0.11	5	113	1409	10	6.23	0.01	26.27	924	<2	0.02	2170	<10	<2	2	<0.01	13	<10	41
46192	<1	0.12	<10	<0.5	<5	0.05	5	111	2407	8	6.27	0.01	25.84	905	<2	0.02	2018	<10	<2	1	<0.01	14	<10	47
46193	<1	0.09	<10	<0.5	<5	0.11	5	110	1362	13	6.05	0.01	27.74	927	<2	0.02	2101	<10	<2	2	<0.01	10	<10	37
46194	<1	0.08	13	<0.5	<5	0.11	6	118	1778	12	6.89	<0.01	25.50	996	<2	0.02	2047	<10	<2	2	<0.01	11	<10	43
46195	1	0.09	<10	<0.5	<5	0.34	6	117	1745	17	6.79	0.01	26.54	991	<2	0.02	2148	<10	<2	4	<0.01	11	<10	46
46196	<1	0.11	<10	<0.5	<5	0.19	5	110	1573	11	6.08	0.01	25.77	902	<2	0.02	2129	<10	<2	3	<0.01	12	<10	40
46197	<1	0.08	<10	<0.5	<5	0.33	6	117	1426	10	6.70	0.01	27.72	1076	<2	0.02	2286	<10	3	9	<0.01	12	<10	47
46198	<1	0.09	<10	<0.5	<5	0.39	5	106	1210	16	5.62	0.01	26.11	834	<2	0.02	2004	<10	<2	13	<0.01	11	<10	37
46199	<1	0.12	<10	<0.5	<5	0.26	6	114	1969	23	6.91	0.01	26.14	924	<2	0.02	2208	<10	<2	4	<0.01	14	<10	45
46200	<1	0.10	<10	<0.5	<5	0.31	5	106	1151	13	5.86	0.01	25.12	887	<2	0.02	2073	<10	<2	8	<0.01	13	<10	39
Duplicates:																								
46101	2	0.12	11	<0.5	<5	0.38	4	108	995	6	5.95	0.01	26.48	901	<2	0.02	2016	<10	<2	18	<0.01	12	<10	50
46110	<1	0.11	<10	<0.5	<5	0.42	4	116	1687	3	5.85	0.01	27.44	1317	<2	0.02	2052	27	<2	19	<0.01	12	<10	66
46120	<1	3.39	40	<0.5	<5	0.97	4	87	1110	60	6.82	0.16	23.77	1024	<2	0.05	1186	458	7	17	0.16	97	<10	79
46123	<1	0.08	<10	<0.5	8	0.26	3	124	2063	6	5.42	<0.01	27.06	947	<2	0.01	2311	10	8	12	<0.01	6	<10	38
46132	<1	0.12	<10	<0.5	8	0.09	4	115	1908	1	6.23	0.01	27.14	890	<2	0.02	2210	<10	8	6	<0.01	12	<10	35
46142	<1	0.24	22	<0.5	9	2.17	4	116	1681	2	6.10	0.02	26.14	978	<2	0.03	2222	28	17	90	0.01	19	<10	35
46145	<1	0.15	14	<0.5	11	1.81	4	118	2335	2	6.79	0.01	23.98	946	<2	0.03	1991	<10	3	48	<0.01	13	<10	50
46154	<1	0.09	<10	<0.5	9	0.10	5	138	1145	6	6.40	<0.01	29.12	936	<2	0.01	2245	<10	3	6	<0.01	10	<10	22
46164	<1	0.16	<10	<0.5	10	0.20	4	122	2171	1	6.99	<0.01	26.85	772	<2	0.02	2047	<10	7	12	<0.01	11	<10	38
46167	<1	7.38	1731	4.3	<5	4.84	2	34	228	25	6.26	3.66	3.75	1052	2	2.61	53	2929	33	974	0.56	161	<10	95
46176	<1	0.09	<10	<0.5	<5	0.24	5	104	1382	3	6.09	<0.01	27.31	878	<2	0.02	1858	<10	<2	7	<0.01	11	<10	50
46186	<1	0.08	12	<0.5	<5	1.64	5	94	1777	12	6.62	<0.01	24.35	1301	<2	0.02	1806	<10	<2	81	<0.01	12	<10	76
46189	<1	0.12	<10	<0.5	<5	0.18	5	113	1314	8	6.47	0.01	25.90	934	<2	0.02	2085	<10	2	4	<0.01	16	<10	41
46198	<1	0.09	<10	<0.5	<5	0.39	5	109	1251	13	5.54	0.01	25.64	854	<2	0.02	2043	<10	<2	14	<0.01	12	<10	39
Standards:																								
Blank	<1	<0.01	<10	<0.5	<5	<0.01	<1	1	2	<1	0.01	<0.01	0.02	<5	<2	0.01	<1	<10	<2	<1	<0.01	<1	<10	<2
CH	2	7.86	455	1.9	11	2.05	3	32	128	1865	6.04	1.86	1.48	455	3	3.64	46	701	13	187	0.32	94	<10	226

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V3508RR

Date : Nov-06-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type: core

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
46201	<1	0.13	14	<0.5	<5	0.27	4	112	1625	7	5.93	0.02	23.41	897	<2	0.02	2073	<10	<2	8	<0.01	11	<10	42
46202	<1	0.11	<10	<0.5	<5	0.23	5	110	1024	8	5.68	0.01	24.38	884	<2	0.02	2127	<10	<2	8	0.01	8	<10	41
46203	<1	0.19	14	<0.5	<5	0.44	6	119	1667	7	6.40	0.02	25.03	1130	<2	0.03	2177	<10	<2	13	<0.01	14	<10	57
46204	<1	0.17	<10	<0.5	<5	0.43	5	108	1486	24	5.99	0.01	23.70	1026	<2	0.02	2150	<10	<2	11	<0.01	14	<10	54
46205	<1	0.17	<10	<0.5	<5	0.25	5	107	1276	27	5.50	0.01	24.10	840	<2	0.02	2120	<10	<2	9	<0.01	15	<10	43
46206	<1	0.17	<10	<0.5	<5	0.30	5	112	1780	20	5.92	0.01	25.23	933	<2	0.02	2252	<10	<2	13	<0.01	12	<10	50
46207	<1	8.66	2385	4.9	<5	6.10	4	63	230	20	9.10	2.52	6.06	2429	3	1.78	159	6270	136	1530	0.92	204	11	239
46208	<1	0.39	45	<0.5	<5	0.95	5	113	1649	11	6.16	0.06	24.50	964	<2	0.05	2168	179	<2	61	0.03	16	<10	63
46209	<1	1.06	157	<0.5	<5	1.05	4	111	1820	20	6.20	0.13	23.35	1325	<2	0.07	1914	637	<2	103	0.10	33	<10	90
46210	<1	0.21	<10	<0.5	<5	0.28	4	104	1617	12	5.61	0.02	23.60	836	<2	0.02	2012	<10	<2	8	<0.01	14	<10	48
46211	<1	0.18	<10	<0.5	<5	0.34	5	105	1242	11	5.66	0.01	23.71	833	<2	0.02	2098	<10	<2	8	0.01	14	<10	44
46212	<1	0.18	<10	<0.5	<5	0.25	5	108	1535	9	5.79	0.01	24.64	936	<2	0.02	2216	<10	<2	7	<0.01	14	<10	45
46213	<1	0.15	<10	<0.5	<5	0.61	4	103	1295	5	5.62	0.01	23.80	961	<2	0.02	2006	<10	<2	17	<0.01	13	<10	42
46214	<1	0.14	<10	<0.5	<5	0.14	5	115	1231	5	6.01	0.01	25.67	957	<2	0.02	2159	<10	<2	3	<0.01	10	<10	38
46215	<1	0.16	<10	<0.5	<5	0.10	5	106	1119	4	5.82	0.01	25.45	808	<2	0.02	2132	<10	<2	2	<0.01	13	<10	34
46216	<1	0.12	<10	<0.5	<5	0.23	5	112	1362	6	5.77	0.01	25.00	923	<2	0.02	2211	<10	<2	4	<0.01	9	<10	38
46217	<1	0.12	<10	<0.5	<5	0.42	5	100	1172	7	5.43	0.01	23.10	842	<2	0.02	1987	<10	<2	23	<0.01	10	<10	57
46218	<1	0.14	<10	<0.5	<5	0.30	5	109	1491	3	5.76	0.01	24.84	845	<2	0.02	2142	<10	<2	14	0.01	11	<10	39
46219	<1	0.13	<10	<0.5	<5	0.33	5	110	1551	3	6.33	0.01	24.64	923	<2	0.02	2085	<10	<2	6	<0.01	10	<10	39
46220	<1	0.15	<10	<0.5	<5	0.12	5	113	1839	2	6.14	0.01	25.59	970	<2	0.02	2141	<10	<2	3	<0.01	11	<10	41
46221	<1	0.11	<10	<0.5	<5	0.10	5	113	1368	1	5.95	0.01	25.43	838	<2	0.02	2128	<10	<2	3	<0.01	8	<10	36
46222	<1	0.17	<10	<0.5	<5	0.18	5	119	2071	1	6.60	0.01	25.12	902	<2	0.02	2197	<10	<2	7	0.01	12	<10	48
46223	<1	0.13	<10	<0.5	<5	0.39	4	100	1289	1	4.76	0.02	23.30	1223	<2	0.02	2293	<10	<2	21	<0.01	11	<10	42
46224	<1	0.06	<10	<0.5	<5	0.22	4	105	1568	3	5.26	0.01	24.53	939	<2	0.02	2255	<10	<2	7	<0.01	10	<10	42
46225	<1	0.07	<10	<0.5	<5	0.26	4	111	1784	<1	5.32	0.01	24.45	954	<2	0.02	2220	<10	2	8	<0.01	8	<10	44
46226	<1	0.10	<10	<0.5	<5	0.22	4	107	1172	<1	4.94	0.01	24.83	832	<2	0.02	2329	<10	<2	11	<0.01	8	<10	33
46227	<1	0.09	<10	<0.5	<5	0.12	4	102	1793	<1	5.37	0.01	22.31	772	<2	0.02	2118	<10	<2	6	<0.01	10	<10	36
46228	<1	0.06	<10	<0.5	<5	0.27	4	106	1047	<1	5.19	0.01	21.93	962	<2	0.02	2208	<10	<2	22	<0.01	9	<10	30
46229	<1	0.05	<10	<0.5	<5	0.13	4	98	878	1	5.23	0.01	23.57	817	<2	0.01	2208	<10	<2	8	<0.01	8	<10	31
46230	<1	0.06	10	<0.5	<5	0.18	4	101	984	<1	5.10	0.01	24.13	976	<2	0.01	2219	<10	<2	7	<0.01	8	<10	29

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V3508RR

Date : Nov-06-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type: core

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
46231	<1	0.09	<10	<0.5	<5	0.19	5	107	1159	<1	5.42	0.01	22.60	814	<2	0.02	2260	<10	<2	4	<0.01	11	<10	27
46232	<1	0.10	<10	<0.5	<5	0.11	4	98	890	<1	5.14	0.01	23.71	761	<2	0.02	2231	<10	<2	3	<0.01	12	<10	21
46233	<1	0.12	<10	<0.5	<5	0.08	4	101	1225	<1	5.02	0.01	22.34	824	<2	0.02	2226	<10	<2	3	<0.01	13	<10	26
46234	<1	2.95	311	1.2	<5	1.46	5	88	1167	1	7.21	0.38	15.87	3005	<2	0.22	1314	1239	15	153	0.26	75	<10	145
46235	<1	0.10	<10	<0.5	<5	0.06	4	101	1105	1	5.24	0.01	22.55	758	<2	0.03	2151	<10	<2	3	<0.01	12	<10	26
46236	<1	0.09	<10	<0.5	<5	0.02	4	99	1015	<1	5.14	0.01	22.44	778	<2	0.02	2107	<10	<2	2	<0.01	10	<10	20
46237	<1	0.10	<10	<0.5	<5	<0.01	4	111	1744	<1	5.43	0.01	23.45	825	<2	0.02	2080	<10	<2	1	<0.01	13	<10	29
46238	<1	0.11	<10	<0.5	<5	0.01	4	98	1502	<1	5.20	0.01	24.50	740	<2	0.03	2052	<10	<2	2	<0.01	13	<10	29
46239	<1	0.13	<10	<0.5	<5	0.05	5	119	1556	<1	6.08	0.01	27.07	908	<2	0.03	2559	<10	<2	2	<0.01	13	<10	34
46240	<1	0.13	<10	<0.5	<5	0.06	5	124	1581	<1	6.68	0.01	27.17	969	<2	0.02	2512	<10	<2	1	<0.01	15	<10	37
46241	<1	0.14	<10	<0.5	<5	0.10	5	121	2281	<1	6.18	0.01	26.81	1045	<2	0.02	2410	<10	<2	3	<0.01	11	<10	49
46242	<1	0.11	<10	<0.5	<5	0.01	2	107	1303	8	6.30	0.01	28.64	914	<2	0.02	2264	10	10	1	<0.01	25	<10	28
46243	<1	0.10	<10	<0.5	<5	0.22	5	114	1299	<1	6.05	0.01	25.81	838	<2	0.02	2374	<10	<2	5	<0.01	13	<10	33
46244	<1	0.09	<10	<0.5	<5	0.27	5	103	1264	1	5.92	0.01	23.99	822	<2	0.02	2134	<10	<2	20	<0.01	13	<10	31
46245	<1	0.16	10	<0.5	<5	0.10	5	118	1757	2	6.24	0.01	26.82	849	<2	0.02	2031	<10	<2	4	<0.01	13	<10	38
46246	<1	0.10	<10	<0.5	<5	0.21	4	121	906	1	5.68	0.01	28.67	900	<2	0.02	2184	<10	<2	7	<0.01	11	<10	34
46247	<1	0.13	<10	<0.5	<5	1.42	5	102	1000	205	5.32	0.01	26.39	1025	<2	0.02	1781	<10	833	69	<0.01	12	<10	166
46248	<1	0.14	<10	<0.5	<5	0.31	5	132	984	3	6.24	0.01	30.48	1011	<2	0.02	2295	<10	<2	8	<0.01	14	<10	47
46249	<1	0.10	<10	<0.5	<5	0.39	5	131	1002	1	6.92	0.01	30.75	1083	2	0.02	2422	<10	<2	8	<0.01	13	<10	40
46250	<1	0.50	56	<0.5	<5	0.33	5	129	1126	4	6.89	0.23	28.42	985	<2	0.17	2246	65	<2	35	0.02	14	<10	40
46251	<1	0.23	23	<0.5	<5	0.58	4	120	786	5	6.08	0.08	27.60	952	<2	0.07	2080	20	<2	17	0.01	11	<10	31
46252	<1	0.09	<10	<0.5	<5	0.46	5	121	1152	3	6.76	0.01	27.78	1006	<2	0.01	2115	<10	<2	18	<0.01	10	<10	35
46253	<1	0.09	<10	<0.5	<5	0.13	5	119	722	2	6.23	0.01	28.44	916	<2	0.02	2021	<10	<2	5	<0.01	11	<10	29
46254	<1	0.10	<10	<0.5	<5	0.08	5	121	1094	4	6.41	<0.01	28.76	866	<2	0.02	2020	<10	<2	4	<0.01	11	<10	33
46255	<1	0.10	<10	<0.5	<5	0.17	5	121	842	2	6.36	0.01	28.15	916	<2	0.01	2088	<10	<2	8	<0.01	10	<10	30
46256	<1	0.12	<10	<0.5	<5	0.23	5	117	1034	2	6.50	<0.01	27.91	892	<2	0.01	2027	<10	<2	4	<0.01	12	<10	32
46257	<1	0.06	10	<0.5	<5	0.29	5	124	536	4	6.03	<0.01	28.43	966	<2	0.01	2121	<10	<2	15	<0.01	7	<10	27
46258	<1	0.11	<10	<0.5	<5	0.20	5	115	823	4	6.17	<0.01	28.09	859	<2	0.02	2012	<10	<2	8	<0.01	11	<10	29
46259	<1	0.13	<10	<0.5	<5	0.13	4	109	783	15	5.96	0.01	27.11	799	<2	0.02	1975	<10	<2	4	<0.01	12	<10	26
46260	<1	0.11	<10	<0.5	<5	0.17	4	113	643	9	5.87	<0.01	26.58	814	<2	0.02	2010	<10	<2	3	<0.01	11	<10	26

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type: core

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V3508RR

Date : Nov-06-08

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
46261	<1	0.10	<10	<0.5	<5	0.11	5	111	721	5	6.15	<0.01	27.49	830	<2	0.02	1940	<10	<2	2	<0.01	11	<10	27
46262	<1	0.10	<10	<0.5	<5	0.15	4	112	671	10	5.95	0.01	27.37	793	<2	0.02	2080	<10	<2	7	<0.01	10	<10	26
46263	<1	0.13	<10	<0.5	<5	0.12	4	109	1583	4	5.63	<0.01	27.12	874	<2	0.02	1919	<10	<2	3	<0.01	9	<10	37
46264	<1	0.10	<10	<0.5	<5	0.28	4	110	1588	4	6.00	<0.01	27.68	872	<2	0.02	2064	<10	<2	5	<0.01	7	<10	38
46265	<1	0.09	<10	<0.5	<5	0.16	4	113	930	4	5.65	0.01	27.85	839	<2	0.01	2060	<10	<2	5	<0.01	7	<10	31
46266	<1	0.09	<10	<0.5	<5	0.08	4	118	1615	7	6.36	0.01	27.67	914	<2	0.01	2031	<10	<2	5	<0.01	7	<10	42
46267	<1	0.10	<10	<0.5	<5	0.07	4	115	1682	8	6.04	0.01	26.90	948	<2	0.01	2054	<10	<2	4	<0.01	8	<10	43
46268	<1	0.13	<10	<0.5	<5	0.50	4	116	2343	9	5.56	0.01	25.91	1098	<2	0.01	2020	23	<2	22	<0.01	10	<10	65
46269	<1	0.07	<10	<0.5	<5	0.40	5	110	821	7	6.13	<0.01	25.43	1126	<2	<0.01	2138	<10	<2	15	<0.01	9	<10	37
46270	<1	0.15	<10	<0.5	<5	0.26	5	149	3083	8	7.49	<0.01	29.18	1305	<2	0.01	2336	<10	<2	8	<0.01	14	<10	88
46271	<1	0.14	<10	<0.5	<5	0.19	4	117	1539	5	6.30	<0.01	27.73	1059	<2	0.01	2154	<10	<2	4	<0.01	12	<10	46
46272	<1	0.10	<10	<0.5	<5	0.16	5	118	1287	6	6.64	<0.01	28.00	960	<2	0.01	2161	<10	<2	3	<0.01	11	<10	39
46273	<1	0.09	<10	<0.5	<5	0.18	4	111	709	5	5.92	<0.01	27.34	826	<2	0.01	2137	<10	<2	4	<0.01	11	<10	28
46274	<1	0.12	<10	<0.5	<5	0.34	4	112	1298	6	6.24	0.01	27.51	931	<2	0.01	2163	<10	<2	23	<0.01	11	<10	38
46275	<1	0.12	<10	<0.5	<5	0.38	4	110	1268	2	5.69	<0.01	25.90	834	<2	0.01	2112	<10	<2	24	<0.01	12	<10	38
46276	<1	0.11	<10	<0.5	<5	0.15	4	107	1378	2	5.14	<0.01	24.50	958	<2	0.01	2120	<10	<2	12	<0.01	9	<10	44
46277	<1	0.11	<10	<0.5	<5	0.28	5	114	1574	2	6.80	<0.01	26.57	891	<2	0.01	2046	<10	<2	13	<0.01	11	<10	46
46278	<1	0.09	<10	<0.5	<5	0.18	4	112	1001	3	5.56	<0.01	27.11	828	<2	0.01	2114	<10	<2	12	<0.01	9	<10	36
46279	<1	0.12	<10	<0.5	<5	0.08	4	104	708	2	5.56	<0.01	26.56	780	<2	0.01	2032	<10	<2	4	<0.01	12	<10	32
46280	<1	0.09	<10	<0.5	<5	0.34	4	108	1129	2	5.51	<0.01	26.71	904	<2	0.01	2085	<10	<2	9	<0.01	8	<10	40
46281	<1	0.11	<10	<0.5	<5	0.49	5	117	1496	2	6.80	<0.01	27.75	1044	<2	0.01	2120	<10	<2	15	<0.01	9	<10	44
46282	<1	0.09	<10	<0.5	<5	0.20	4	114	1084	3	6.15	<0.01	27.40	914	<2	0.01	2114	<10	<2	8	<0.01	11	<10	38
46283	<1	0.09	11	<0.5	<5	0.46	4	104	1017	8	5.57	0.01	25.37	911	<2	0.01	1839	12	117	30	<0.01	9	<10	49
46284	<1	0.09	10	<0.5	<5	0.20	5	114	999	3	6.12	0.01	26.91	850	<2	0.01	2110	<10	<2	8	<0.01	8	<10	38
46285	<1	0.07	<10	<0.5	<5	0.16	4	117	1002	3	5.87	0.01	26.73	1005	<2	0.01	2116	<10	<2	10	<0.01	7	<10	37
46286	<1	0.07	<10	<0.5	<5	0.19	4	113	1178	2	5.79	<0.01	26.18	912	<2	0.01	2022	<10	<2	9	<0.01	6	<10	37
46287	<1	0.11	<10	<0.5	<5	0.12	4	112	1210	2	5.72	0.01	27.52	884	<2	0.01	2040	<10	<2	4	<0.01	10	<10	34
46288	<1	0.12	<10	<0.5	<5	0.12	4	110	1020	2	5.86	0.01	26.92	873	<2	0.01	2019	<10	<2	4	<0.01	11	<10	38
46289	<1	0.10	<10	<0.5	<5	0.30	6	120	1510	4	6.66	0.01	28.40	965	<2	0.01	2064	<10	<2	10	<0.01	6	<10	47
46290	<1	0.10	<10	<0.5	<5	0.19	4	119	2150	7	5.67	0.01	28.60	1010	3	0.02	2080	<10	<2	10	<0.01	3	<10	56

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type: core

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V3508RR

Date : Nov-06-08

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
46291	<1	0.07	<10	<0.5	<5	0.22	5	116	901	8	5.43	0.01	28.50	925	9	0.02	2008	<10	<2	9	<0.01	4	<10	38
46292	<1	0.06	<10	<0.5	<5	0.36	5	117	745	6	5.42	0.01	27.70	910	4	0.02	2080	<10	<2	23	<0.01	4	<10	39
46293	<1	0.06	<10	<0.5	<5	0.17	5	116	728	4	5.42	0.01	28.20	911	2	0.02	2064	<10	10	7	<0.01	4	<10	41
46294	<1	0.10	10	<0.5	<5	0.27	5	119	1290	3	6.18	0.01	29.20	1000	<2	0.02	2088	<10	4	16	<0.01	6	<10	51
46295	<1	0.09	<10	<0.5	<5	0.61	5	115	1260	3	5.69	0.01	27.70	962	<2	0.03	1944	<10	<2	30	<0.01	5	<10	47
46296	<1	0.08	<10	<0.5	<5	0.34	6	129	1530	3	6.66	0.01	31.10	1090	<2	0.02	2168	<10	<2	11	<0.01	7	<10	53
46297	<1	0.09	<10	<0.5	<5	0.43	5	113	1470	6	5.61	0.01	28.70	997	2	0.02	2024	<10	<2	6	<0.01	5	<10	43
46298	<1	2.08	546	0.7	<5	1.72	4	100	1710	17	6.28	0.98	21.30	1010	9	0.47	1432	878	<2	450	0.17	51	<10	64
46299	<1	0.10	<10	<0.5	<5	0.47	5	110	1200	5	5.82	0.01	26.80	933	5	0.02	1888	<10	<2	12	<0.01	8	<10	35
46300	<1	0.12	<10	<0.5	<5	0.33	5	122	910	2	5.73	0.01	27.80	857	<2	0.02	2032	<10	<2	14	<0.01	10	<10	30
46301	<1	0.12	<10	<0.5	<5	0.13	5	109	1400	2	5.77	0.01	28.20	884	<2	0.03	1912	<10	<2	7	<0.01	8	<10	36
46302	<1	0.12	<10	<0.5	<5	0.22	5	117	1330	2	6.05	0.01	29.50	984	<2	0.02	1992	<10	<2	11	<0.01	9	<10	39
46303	<1	0.14	<10	<0.5	<5	0.24	5	112	1670	1	6.03	0.01	28.50	816	2	0.02	1944	<10	<2	12	<0.01	9	<10	42
46304	<1	0.13	<10	<0.5	<5	0.22	5	116	1470	3	6.31	0.01	29.20	836	2	0.02	2032	<10	<2	9	<0.01	8	<10	38
46305	<1	0.09	<10	<0.5	<5	0.49	5	118	1210	5	5.74	0.01	27.40	982	5	0.02	2080	<10	<2	22	<0.01	8	<10	41
46306	<1	0.12	<10	<0.5	<5	0.23	5	117	1320	8	5.74	0.01	28.40	901	5	0.02	2056	<10	<2	14	<0.01	7	<10	38
46307	<1	2.08	11	<0.5	<5	0.75	6	109	1110	3	7.91	0.01	23.50	2620	2	0.02	1592	1421	<2	24	0.22	52	<10	112
46308	<1	0.15	<10	<0.5	<5	0.41	5	108	1340	2	5.76	0.01	26.40	961	<2	0.02	1856	<10	<2	20	<0.01	11	<10	39
46309	<1	0.16	<10	<0.5	<5	0.19	5	114	1360	2	6.17	0.01	27.00	810	<2	0.02	1936	<10	<2	8	<0.01	11	<10	36
46310	<1	0.15	<10	<0.5	<5	0.35	5	118	1890	1	6.15	0.01	28.20	966	<2	0.02	2048	<10	<2	19	<0.01	11	<10	45
46311	<1	0.15	<10	<0.5	<5	0.27	4	116	1708	3	5.99	<0.01	23.30	890	<2	0.02	2171	<10	3	13	<0.01	14	<10	68
46312	<1	0.17	<10	<0.5	<5	0.33	4	110	1221	2	5.66	<0.01	23.47	808	<2	0.02	2010	<10	3	14	<0.01	17	<10	61
46313	<1	0.20	27	<0.5	<5	0.38	4	111	1340	2	5.76	0.01	23.30	827	<2	0.02	2004	<10	3	30	0.01	18	<10	59
46314	<1	0.15	<10	<0.5	<5	0.52	4	111	1601	2	5.87	<0.01	22.32	808	<2	0.02	1836	<10	3	30	<0.01	14	<10	63
46315	<1	0.13	<10	<0.5	<5	0.46	4	112	976	3	5.80	0.01	23.96	880	<2	0.02	1996	<10	4	26	<0.01	13	<10	61
46316	<1	0.24	22	<0.5	<5	0.49	4	115	1546	2	5.90	0.01	21.59	930	<2	0.03	2020	<10	2	27	0.01	19	<10	63
46317	<1	0.31	<10	<0.5	<5	0.12	4	116	1386	3	5.94	0.01	22.16	711	<2	0.04	2053	<10	3	12	0.01	19	<10	57
46318	<1	4.98	951	1.6	<5	1.14	4	90	845	7	7.49	0.73	16.15	2267	<2	0.33	1260	1702	138	329	0.29	87	<10	237
46319	<1	0.42	29	<0.5	<5	0.54	4	116	1192	1	6.10	0.02	23.08	929	<2	0.02	1997	107	4	36	0.03	20	<10	61
46320	<1	0.26	17	<0.5	<5	0.59	4	110	1046	2	5.71	0.01	22.50	910	<2	0.02	1981	<10	4	23	0.01	15	<10	62

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V3508RR

Date : Nov-06-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type: core

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
46321	<1	0.26	<10	<0.5	<5	0.49	4	112	1215	4	6.02	0.01	23.14	842	<2	0.02	2041	<10	4	18	0.01	17	<10	58
46322	<1	0.26	<10	<0.5	<5	0.55	4	115	1401	2	5.62	<0.01	23.02	836	<2	0.02	1965	<10	2	37	0.01	15	<10	59
46323	<1	0.30	<10	<0.5	<5	0.40	4	108	1514	2	5.81	<0.01	22.56	737	<2	0.02	1922	<10	5	12	0.01	17	<10	62
46324	<1	0.29	<10	<0.5	<5	0.65	4	109	1381	2	6.00	<0.01	22.55	827	<2	0.01	1932	<10	2	17	0.01	17	<10	58
46325	<1	0.32	13	<0.5	<5	0.16	5	106	1493	2	6.16	<0.01	21.05	719	<2	0.02	1895	54	8	8	0.01	21	<10	58
46326	<1	0.28	<10	<0.5	<5	0.45	4	109	1494	1	5.71	<0.01	21.71	770	<2	0.01	1906	17	<2	28	0.01	16	<10	54
46327	<1	0.28	<10	<0.5	<5	0.25	4	109	1193	1	5.80	<0.01	23.00	780	<2	0.01	1978	<10	4	9	0.01	15	<10	50
46328	<1	0.20	<10	<0.5	<5	0.15	4	115	1238	1	6.07	<0.01	22.99	764	<2	0.01	1973	<10	<2	5	0.01	14	<10	50
46329	<1	0.32	<10	<0.5	<5	0.13	4	110	1334	1	5.87	<0.01	22.66	735	<2	0.02	1845	<10	2	3	0.01	16	<10	50
46330	<1	0.31	<10	<0.5	<5	0.18	4	109	1536	1	6.07	<0.01	23.21	758	<2	0.02	1846	<10	2	5	0.01	16	<10	51
46331	<1	0.35	<10	<0.5	<5	0.16	4	107	1543	2	6.19	<0.01	22.08	743	<2	0.02	1878	<10	2	5	0.01	19	<10	53
46332	<1	0.33	13	<0.5	<5	0.29	4	110	1724	50	6.09	<0.01	22.00	750	<2	0.02	1902	41	34	12	0.01	21	<10	91
46333	<1	0.28	13	<0.5	<5	0.45	5	109	1564	7	5.69	0.01	26.61	970	<2	0.02	1905	46	32	13	0.01	21	<10	76
46334	<1	0.28	<10	<0.5	<5	0.38	5	114	1296	1	5.81	0.01	27.61	948	<2	0.02	2017	<10	6	11	0.01	16	<10	39
46335	<1	0.35	<10	<0.5	<5	0.26	6	130	1545	<1	6.72	0.01	29.52	963	<2	0.02	2288	10	4	18	0.01	22	<10	46
46336	<1	0.34	<10	<0.5	<5	1.06	5	115	1583	2	5.93	0.01	26.42	1050	<2	0.02	2034	54	21	58	0.01	21	<10	54
46337	<1	0.29	<10	<0.5	<5	0.33	5	123	1480	<1	5.99	0.01	29.57	940	<2	0.02	2206	14	11	20	0.01	16	<10	41
46338	<1	0.25	<10	<0.5	<5	0.35	6	128	1624	<1	6.62	0.01	30.16	1068	<2	0.02	2148	<10	<2	11	0.01	16	<10	48
46339	<1	0.36	<10	<0.5	<5	0.48	6	131	1887	1	6.74	0.01	30.56	998	2	0.03	2238	15	12	20	0.01	20	<10	49
46340	<1	9.46	19	3.2	<5	3.06	10	77	595	<1	>15.00	0.13	12.33	9237	2	0.31	313	4177	76	341	0.82	260	22	514
46341	<1	0.43	<10	<0.5	<5	0.93	5	120	1694	<1	5.88	0.02	27.18	1118	2	0.03	2046	30	11	39	0.02	18	<10	67
46342	<1	0.40	<10	<0.5	<5	0.32	6	130	1563	1	6.53	0.01	28.65	1161	<2	0.02	2247	52	6	12	0.02	21	<10	56
46343	<1	0.30	<10	<0.5	<5	0.20	5	126	1627	3	6.24	0.01	28.27	974	<2	0.02	2205	<10	16	12	0.01	19	<10	45
46344	<1	0.37	<10	<0.5	<5	0.22	5	121	1862	2	6.38	0.01	28.84	986	<2	0.02	2014	<10	3	8	0.01	20	<10	44
46345	<1	0.38	<10	<0.5	<5	0.29	5	128	2124	4	6.18	0.01	29.26	997	<2	0.02	2247	<10	17	7	0.01	21	<10	47
46346	<1	0.41	<10	<0.5	<5	0.65	5	131	4099	2	6.63	0.01	29.90	1092	<2	0.02	2235	21	4	14	0.02	21	<10	79
46347	<1	0.39	<10	<0.5	<5	0.24	6	134	1921	1	6.62	0.01	31.09	1070	<2	0.02	2336	<10	19	6	0.02	21	<10	49
46348	<1	0.41	<10	<0.5	<5	0.45	5	133	1944	2	6.54	0.01	30.44	1016	<2	0.02	2193	19	<2	16	0.02	22	<10	48
46349	<1	0.34	<10	<0.5	<5	0.51	6	134	1828	2	6.43	0.01	31.50	1130	<2	0.02	2249	17	4	21	0.01	19	<10	49
46350	<1	0.44	<10	<0.5	<5	0.70	6	133	1932	4	6.75	0.01	31.62	1163	<2	0.02	2263	23	8	27	0.02	22	<10	62

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type: core

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V3508RR

Date : Nov-06-08

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
46351	<1	0.42	<10	<0.5	<5	0.91	11	124	1908	35	6.40	0.01	27.95	1074	<2	0.02	2115	18	149	33	0.02	22	12	636
46352	<1	0.38	<10	<0.5	<5	0.36	6	132	1950	1	6.40	0.01	28.64	1085	<2	0.02	2290	<10	2	11	0.02	21	<10	50
46353	<1	0.18	51	<0.5	<5	0.94	5	102	1269	24	5.01	0.02	24.05	1915	<2	0.02	1920	18	43	41	<0.01	25	<10	78
46354	<1	0.11	<10	<0.5	<5	1.70	5	123	2168	14	6.00	0.01	26.88	2289	<2	0.02	2086	<10	31	93	<0.01	12	<10	107
46355	<1	0.09	<10	<0.5	<5	0.60	4	92	1089	12	4.79	<0.01	22.46	1073	<2	<0.01	2058	<10	<2	32	<0.01	7	<10	53
46356	<1	0.15	<10	<0.5	<5	0.63	5	104	1019	24	5.55	<0.01	26.38	887	<2	0.01	2225	<10	<2	27	<0.01	12	<10	43
46357	<1	0.15	<10	<0.5	<5	0.56	5	99	1135	11	5.43	<0.01	25.43	841	<2	0.02	2175	<10	<2	43	<0.01	12	<10	39
46360	<1	0.18	<10	<0.5	<5	0.55	5	108	1415	4	5.88	<0.01	28.22	888	<2	0.02	2339	<10	<2	19	<0.01	15	<10	40
46361	<1	0.18	<10	<0.5	<5	0.43	5	106	1291	11	5.97	<0.01	28.46	786	<2	0.03	2388	<10	<2	19	<0.01	15	<10	39
46362	<1	0.16	<10	<0.5	<5	0.55	5	106	1227	4	5.76	<0.01	26.71	876	<2	0.03	2298	<10	<2	18	<0.01	14	<10	36
46363	<1	0.18	<10	<0.5	<5	0.38	5	100	1085	8	5.74	<0.01	26.65	824	<2	0.03	2222	<10	<2	12	<0.01	17	<10	35
46364	<1	0.15	<10	<0.5	<5	0.43	5	99	898	9	5.24	<0.01	24.06	802	<2	0.02	2183	<10	<2	19	<0.01	14	<10	30
46365	<1	0.14	10	<0.5	<5	1.28	5	97	1157	18	5.50	<0.01	25.39	981	<2	0.02	2105	12	<2	61	<0.01	13	<10	37
46366	<1	0.12	<10	<0.5	<5	0.08	5	116	844	19	5.30	<0.01	28.02	870	<2	0.02	2621	<10	<2	6	<0.01	10	<10	38
46367	<1	0.12	<10	<0.5	<5	1.00	5	110	998	12	5.60	<0.01	25.57	816	<2	0.02	2389	12	<2	38	<0.01	11	<10	48
46368	<1	0.08	<10	<0.5	<5	0.81	5	108	892	4	5.63	<0.01	27.88	932	<2	0.01	2353	<10	<2	14	<0.01	5	<10	51
46369	<1	0.10	<10	<0.5	<5	0.54	6	118	1161	3	6.43	0.01	28.96	1036	<2	0.02	2491	<10	<2	20	<0.01	9	<10	53
46372	<1	0.12	<10	<0.5	<5	0.25	5	111	1123	4	5.72	0.01	25.72	854	<2	0.02	2400	<10	<2	16	<0.01	12	<10	43
46373	<1	0.10	<10	<0.5	<5	0.48	5	102	1212	3	5.51	<0.01	26.46	854	<2	0.02	2129	<10	<2	19	<0.01	11	<10	39
46374	<1	0.11	<10	<0.5	<5	0.12	5	108	1088	9	5.60	0.01	26.80	851	<2	0.02	2392	<10	<2	5	<0.01	12	<10	35
46375	<1	0.13	<10	<0.5	<5	0.19	5	107	993	8	5.47	<0.01	26.83	829	<2	0.02	2370	<10	<2	6	<0.01	13	<10	36
46376	<1	0.11	<10	<0.5	<5	0.38	5	102	1444	8	5.84	0.01	26.08	969	<2	0.02	2203	<10	<2	16	<0.01	11	<10	44
46377	<1	0.16	<10	<0.5	<5	0.37	5	101	1923	6	5.84	0.01	26.30	1072	<2	0.02	2193	<10	<2	10	<0.01	12	<10	45
46378	<1	0.17	<10	<0.5	<5	0.21	5	109	1461	11	5.64	0.01	25.83	904	<2	0.02	2265	<10	<2	13	<0.01	13	<10	38
46379	<1	0.16	<10	<0.5	<5	0.47	5	101	1348	8	5.33	0.01	24.43	914	<2	0.02	1934	12	<2	66	<0.01	14	<10	43
46380	<1	0.13	<10	<0.5	<5	0.41	5	100	1215	7	5.14	0.01	24.28	905	<2	0.02	2064	22	<2	180	<0.01	11	<10	38
46381	<1	0.12	26	<0.5	<5	0.60	6	112	1408	7	5.62	0.02	22.03	1053	<2	0.02	2059	27	8	44	<0.01	16	<10	53
46384	<1	0.12	23	<0.5	<5	0.66	8	131	1420	6	6.79	0.03	25.38	1044	<2	0.02	2343	<10	5	32	<0.01	11	<10	62
46385	<1	0.08	13	<0.5	<5	0.25	7	115	1024	6	6.21	0.02	25.37	953	<2	0.02	2167	<10	3	14	<0.01	7	<10	48
46386	<1	0.06	<10	<0.5	<5	0.13	7	119	1087	6	5.77	0.01	26.07	817	<2	0.01	2243	<10	<2	9	<0.01	6	<10	39

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type: core

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V3508RR

Date : Nov-06-08

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
46387	<1	0.11	13	<0.5	<5	0.56	8	129	1592	9	6.73	0.01	25.32	1005	<2	0.02	2123	<10	<2	21	<0.01	9	<10	51
46388	1	0.12	<10	<0.5	<5	0.67	6	106	1268	10	5.94	0.01	24.25	1068	<2	0.03	1520	<10	5	54	<0.01	12	<10	56
46389	<1	0.11	<10	<0.5	<5	0.11	7	122	1634	15	6.87	0.01	25.03	942	<2	0.02	2289	<10	4	8	<0.01	10	<10	58
46390	<1	0.16	<10	<0.5	<5	0.18	6	114	3178	10	6.14	0.02	24.38	1090	<2	0.03	1952	32	11	16	0.01	15	<10	95
46391	<1	0.11	<10	<0.5	<5	0.16	7	112	1377	12	6.36	0.02	25.22	966	<2	0.02	2077	<10	<2	13	<0.01	11	<10	50
46392	<1	0.09	<10	<0.5	<5	0.16	7	116	1167	11	6.10	0.02	25.64	830	<2	0.02	2226	<10	<2	5	<0.01	10	<10	37
46393	<1	0.07	<10	<0.5	<5	0.12	7	123	848	5	6.42	0.02	26.74	802	<2	0.02	2362	<10	2	6	<0.01	8	<10	33
46396	<1	0.11	<10	<0.5	<5	0.05	7	118	1570	9	6.14	0.02	26.06	918	<2	0.02	2175	<10	<2	2	<0.01	9	<10	56
46397	<1	0.13	<10	<0.5	<5	0.25	7	121	1541	4	6.55	0.02	26.92	1031	<2	0.02	2145	<10	<2	7	<0.01	12	<10	53
46398	<1	0.13	<10	<0.5	<5	0.10	7	115	1517	2	5.90	0.02	26.24	918	<2	0.03	2194	<10	<2	3	<0.01	13	<10	50
46399	<1	0.10	<10	<0.5	<5	0.23	8	126	1806	3	7.06	0.01	26.29	965	<2	0.02	2262	<10	<2	6	<0.01	10	<10	46
46400	<1	0.11	<10	<0.5	<5	0.12	8	120	1754	5	6.87	0.01	25.92	908	<2	0.02	2204	<10	<2	5	<0.01	10	<10	41
46358	<1	0.12	<10	<0.5	<5	0.79	6	109	1101	5	5.47	0.01	25.89	874	<2	0.03	2189	<10	<2	43	<0.01	14	<10	37
46359	<1	0.13	<10	<0.5	<5	0.36	7	106	1729	3	5.97	0.02	25.63	821	<2	0.03	1996	<10	<2	24	<0.01	16	<10	55
46370	<1	0.10	<10	<0.5	<5	0.42	7	108	1218	1	5.95	0.02	25.82	1022	<2	0.02	2280	<10	<2	37	<0.01	14	<10	56
46371	<1	0.11	<10	<0.5	<5	0.17	7	120	1268	1	6.13	0.02	27.67	967	<2	0.02	2444	<10	<2	6	<0.01	15	<10	55
46382	<1	0.12	<10	<0.5	<5	0.37	7	115	1603	11	6.16	0.02	26.51	1105	<2	0.02	2353	<10	7	39	<0.01	15	<10	76
46383	<1	0.13	<10	<0.5	<5	0.21	7	122	1329	7	6.01	0.03	27.37	927	6	0.02	2440	<10	<2	14	<0.01	15	11	55
46394	<1	0.09	<10	<0.5	<5	0.13	7	115	811	8	5.92	0.04	27.76	780	<2	0.02	2383	<10	3	6	<0.01	11	<10	37
46395	<1	0.09	<10	<0.5	<5	0.36	6	104	1415	11	5.39	0.04	25.13	1018	<2	0.02	2143	<10	<2	21	<0.01	10	<10	59
Duplicates:																								
46201	<1	0.14	12	<0.5	<5	0.27	5	109	1559	9	6.13	0.02	24.48	859	<2	0.02	2125	<10	<2	8	<0.01	8	<10	46
46210	<1	0.20	<10	<0.5	<5	0.28	5	104	1635	12	5.63	0.02	23.36	842	<2	0.02	2004	<10	<2	8	0.01	14	<10	49
46220	<1	0.15	<10	<0.5	<5	0.11	5	111	1788	3	6.07	0.01	25.09	970	<2	0.02	2081	<10	<2	2	<0.01	11	<10	39
46223	<1	0.11	<10	<0.5	<5	0.40	4	100	1288	1	5.01	0.01	23.77	1238	<2	0.02	2180	<10	<2	19	<0.01	11	<10	48
46232	<1	0.10	<10	<0.5	<5	0.11	4	102	956	<1	5.39	0.01	24.67	788	<2	0.02	2220	<10	<2	3	<0.01	12	<10	27
46242	<1	0.10	<10	<0.5	<5	<0.01	2	109	1152	<1	6.01	0.02	28.42	903	7	0.03	2276	<10	16	1	<0.01	25	<10	25
46245	<1	0.16	<10	<0.5	<5	0.10	5	118	1802	<1	6.58	0.01	28.06	866	<2	0.02	2058	<10	<2	4	<0.01	13	<10	44
46254	<1	0.12	<10	<0.5	<5	0.08	5	118	1071	3	6.40	0.01	28.24	850	<2	0.02	1980	<10	<2	3	<0.01	11	<10	32
46264	<1	0.12	<10	<0.5	<5	0.25	4	114	1554	3	6.21	0.01	27.60	880	<2	0.02	2021	<10	<2	5	<0.01	8	<10	39

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V3508RR

Date : Nov-06-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type: core

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
46267	<1	0.09	<10	<0.5	<5	0.07	4	115	1587	6	6.02	<0.01	27.12	952	<2	0.01	2062	<10	<2	4	<0.01	8	<10	44
46276	<1	0.11	<10	<0.5	<5	0.14	4	107	1316	2	5.35	<0.01	25.83	943	<2	0.01	2086	<10	<2	11	<0.01	9	<10	43
46286	<1	0.04	<10	<0.5	<5	0.21	4	114	1037	2	5.95	<0.01	26.56	925	<2	0.01	2089	<10	<2	10	<0.01	7	<10	36
46289	<1	0.11	<10	<0.5	<5	0.30	6	125	1600	4	6.89	0.02	29.60	991	2	0.03	2168	<10	<2	11	<0.01	7	<10	49
46298	<1	2.10	559	0.7	<5	1.74	4	100	1760	14	6.32	0.99	21.60	1010	4	0.48	1456	876	<2	458	0.17	51	<10	62
46308	<1	0.15	<10	<0.5	<5	0.42	5	111	1250	3	6.16	0.01	27.90	994	3	0.02	1904	<10	<2	20	<0.01	11	<10	37
46311	<1	0.19	<10	<0.5	<5	0.34	5	113	1949	1	5.65	0.01	22.47	924	<2	0.02	2047	<10	5	15	<0.01	17	<10	81
46320	<1	0.26	18	<0.5	<5	0.61	4	112	1043	2	5.92	0.01	23.68	928	<2	0.02	2027	<10	4	23	0.01	15	<10	66
46330	<1	0.33	<10	<0.5	<5	0.19	4	112	1523	2	6.37	<0.01	24.19	775	<2	0.02	1901	<10	<2	5	0.01	17	<10	54
46333	<1	0.28	14	<0.5	<5	0.47	6	114	1578	7	5.56	0.01	27.38	998	<2	0.02	2002	54	36	14	0.01	21	<10	76
46342	<1	0.38	<10	<0.5	<5	0.30	5	124	1501	1	6.19	<0.01	27.78	1111	<2	0.02	2115	40	10	11	0.02	20	<10	50
46352	<1	0.37	<10	<0.5	<5	0.36	6	130	1947	3	6.24	<0.01	28.09	1071	<2	0.02	2125	<10	7	11	0.01	20	<10	50
46355	<1	0.11	<10	<0.5	<5	0.68	5	99	1158	14	5.06	<0.01	23.97	1160	<2	0.01	2170	<10	<2	39	<0.01	8	<10	51
46366	<1	0.12	<10	<0.5	<5	0.07	5	104	931	18	4.78	<0.01	24.46	795	<2	0.02	2324	<10	<2	6	<0.01	9	<10	35
46378	<1	0.17	<10	<0.5	<5	0.20	5	106	1346	12	5.43	0.01	24.92	864	<2	0.02	2173	<10	<2	14	<0.01	14	<10	36
46381	<1	0.12	20	<0.5	<5	0.61	6	108	1444	7	5.80	0.01	22.41	1077	<2	0.02	2031	31	11	46	<0.01	17	<10	54
46392	<1	0.09	<10	<0.5	<5	0.16	7	110	949	10	5.95	0.01	24.89	792	<2	0.02	2132	<10	<2	5	<0.01	9	<10	32
46358	<1	0.12	<10	<0.5	<5	0.82	6	112	1139	3	5.63	0.02	26.48	886	<2	0.03	2253	13	<2	44	<0.01	14	<10	41
Standards:																								
Blank	<1	<0.01	<10	<0.5	<5	<0.01	<1	<1	<1	<1	<0.01	<0.01	<0.01	<5	<2	<0.01	<1	<10	<2	<1	<0.01	<1	<10	<2
CH-4	2	8.35	460	1.4	<5	1.86	3	31	130	2170	5.44	1.80	1.49	458	3	3.30	59	757	15	210	0.34	93	10	213

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V3599RR

Date : Jan-06-09

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type: Core

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
46401	<1	0.07	<10	<0.5	<5	0.10	2	109	1257	4	5.96	0.03	27.39	865	<2	0.02	2144	<10	12	5	<0.01	21	<10	23
46402	1	0.07	<10	<0.5	<5	0.22	3	117	1674	7	7.45	0.02	26.65	1225	<2	0.02	2224	<10	22	7	<0.01	25	<10	33
46403	<1	0.05	<10	<0.5	<5	0.16	3	113	1419	4	6.91	0.01	26.35	904	<2	0.02	2294	<10	24	5	<0.01	24	<10	29
46404	<1	0.05	<10	<0.5	<5	0.18	2	112	1433	9	6.59	0.01	25.72	944	<2	0.02	2167	<10	16	14	<0.01	24	<10	32
46405	2	0.08	<10	<0.5	<5	0.51	2	113	1885	5	6.06	0.02	26.85	1230	<2	0.01	2079	<10	11	16	<0.01	22	<10	50
46406	<1	0.08	<10	<0.5	<5	0.19	2	105	1549	8	5.75	0.01	25.99	1068	<2	0.02	2051	<10	11	8	<0.01	22	<10	37
46407	<1	0.09	<10	<0.5	<5	0.34	2	103	1147	4	5.62	0.03	26.54	1246	<2	0.03	2049	17	11	16	<0.01	24	<10	30
46408	<1	0.10	<10	<0.5	<5	0.12	2	109	1446	1	6.24	0.02	25.94	898	<2	0.02	2185	<10	8	5	<0.01	27	<10	28
46409	<1	0.17	22	<0.5	<5	0.13	2	107	1531	1	5.62	0.07	25.85	846	<2	0.15	2163	<10	7	5	<0.01	23	<10	35
46410	<1	0.07	<10	<0.5	<5	0.15	2	103	1065	1	5.54	0.01	25.51	815	<2	0.02	2051	15	14	6	<0.01	22	<10	25
46411	<1	0.07	<10	<0.5	<5	0.05	2	108	1397	1	5.87	0.01	26.45	895	<2	0.02	2213	<10	13	3	<0.01	22	<10	26
46412	<1	0.04	<10	<0.5	<5	0.05	2	110	1116	2	5.97	0.01	26.37	901	<2	0.01	2246	<10	6	3	<0.01	21	<10	25
46415	<1	0.07	11	<0.5	<5	0.74	2	94	1511	1	5.13	0.02	21.70	1084	<2	0.02	1813	34	7	61	<0.01	23	<10	49
46416	<1	0.09	<10	<0.5	<5	0.19	2	109	1392	<1	6.18	0.01	25.33	922	<2	0.03	2090	14	7	11	<0.01	28	<10	35
46417	<1	0.08	<10	<0.5	<5	0.26	2	107	1189	<1	6.06	0.01	25.37	867	<2	0.02	2111	<10	8	6	<0.01	27	<10	22
46418	<1	0.08	<10	<0.5	<5	0.13	2	110	1280	<1	5.96	0.01	25.45	920	<2	0.02	2194	<10	8	4	<0.01	26	<10	25
46419	<1	0.06	<10	<0.5	<5	0.08	2	112	1484	<1	6.10	0.01	25.03	929	<2	0.02	2050	<10	8	4	<0.01	23	<10	28
46420	<1	0.07	<10	<0.5	<5	0.21	2	105	1795	<1	6.01	0.01	23.97	885	<2	0.02	2018	<10	8	14	<0.01	25	<10	44
46423	<1	0.12	<10	<0.5	<5	0.17	2	104	1278	<1	5.76	0.01	24.20	860	<2	0.02	2065	<10	10	8	<0.01	28	<10	28
46424	<1	0.09	<10	<0.5	<5	0.27	2	109	1321	<1	6.05	0.01	23.37	856	<2	0.02	2098	<10	9	10	<0.01	27	<10	27
46425	<1	0.09	<10	<0.5	<5	0.40	2	109	1456	<1	6.00	0.01	22.92	902	<2	0.01	2111	<10	12	31	<0.01	27	<10	29
46426	<1	0.09	<10	<0.5	<5	0.88	2	98	1281	2	5.66	0.02	23.12	959	<2	0.02	1885	24	10	80	<0.01	26	<10	29
46427	<1	0.17	<10	<0.5	<5	0.67	5	114	1150	3	5.91	0.01	26.14	864	<2	0.03	2241	<10	8	36	<0.01	14	<10	49
46428	<1	1.74	17	<0.5	<5	1.25	5	99	1149	9	6.25	0.04	25.15	926	<2	0.04	1750	211	13	78	0.08	58	<10	61
46429	<1	1.15	17	<0.5	<5	1.64	5	107	1280	12	6.23	0.03	24.78	1039	<2	0.03	1957	163	7	111	0.05	41	<10	61
46430	<1	0.11	15	<0.5	<5	1.23	5	111	1494	3	5.97	0.01	25.60	880	<2	0.02	2192	10	<2	16	<0.01	11	<10	39
46431	<1	0.14	<10	<0.5	<5	0.98	5	109	1480	1	5.81	0.01	26.23	845	<2	0.02	2059	<10	<2	19	<0.01	13	<10	40
46432	<1	0.16	<10	<0.5	<5	1.11	5	107	1532	1	5.51	0.01	25.47	799	<2	0.02	2042	15	4	14	<0.01	13	<10	34
46433	<1	0.13	<10	<0.5	<5	1.62	5	109	1425	1	5.68	0.01	26.35	973	2	0.02	2058	10	<2	83	<0.01	11	<10	34
46434	<1	0.15	<10	<0.5	<5	1.70	5	113	1539	1	5.63	0.01	27.03	1047	<2	0.02	2073	<10	5	83	<0.01	12	<10	36

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V3599RR

Date : Jan-06-09

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type: Core

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
46435	<1	0.10	<10	<0.5	<5	0.89	5	115	1250	<1	5.79	0.01	28.85	930	<2	0.02	2192	<10	<2	26	<0.01	12	<10	33
46436	<1	0.13	<10	<0.5	<5	1.14	5	111	1505	<1	6.07	0.01	29.10	912	<2	0.03	2256	<10	<2	20	<0.01	14	<10	37
46437	<1	0.13	<10	<0.5	<5	1.07	6	117	1585	<1	6.23	0.01	29.68	959	<2	0.03	2213	10	<2	16	<0.01	13	<10	38
46438	<1	0.15	12	<0.5	<5	0.89	6	119	1684	<1	6.21	0.01	28.88	902	<2	0.02	2207	<10	<2	13	<0.01	14	<10	40
46439	<1	0.14	13	<0.5	<5	0.90	6	114	1835	<1	6.38	0.01	30.03	911	<2	0.03	2332	<10	<2	16	<0.01	12	<10	46
46440	<1	0.15	10	<0.5	<5	0.60	6	112	2177	1	6.27	0.01	29.24	929	<2	0.02	2296	<10	<2	14	<0.01	14	<10	48
46441	<1	0.16	18	<0.5	<5	0.56	5	118	2366	1	6.11	0.01	29.20	939	<2	0.03	2252	<10	<2	10	<0.01	15	<10	49
46442	<1	0.13	12	<0.5	<5	0.34	5	108	1955	1	6.30	0.01	29.83	995	<2	0.02	2243	<10	<2	8	<0.01	12	<10	46
46443	<1	0.14	10	<0.5	<5	0.30	6	112	1844	1	6.05	0.01	28.73	944	<2	0.03	2270	<10	<2	10	<0.01	14	<10	44
46444	<1	0.22	40	<0.5	<5	0.59	5	109	2270	1	6.11	0.01	28.75	799	<2	0.04	2070	<10	<2	13	<0.01	19	<10	53
46445	<1	0.15	10	<0.5	<5	1.61	6	105	2068	1	5.93	0.01	26.07	796	<2	0.03	2086	<10	<2	34	<0.01	12	<10	46
46446	<1	0.13	<10	<0.5	<5	1.30	5	104	1962	<1	5.75	0.01	25.64	892	<2	0.03	1985	<10	<2	20	<0.01	12	<10	41
46447	<1	1.98	27	<0.5	<5	1.20	6	111	2039	16	6.94	0.07	22.58	899	<2	0.06	1984	195	5	30	0.10	71	<10	59
46448	<1	4.32	42	0.6	<5	0.49	4	78	1126	26	6.38	0.10	19.81	744	<2	0.23	1248	377	9	23	0.18	107	<10	53
46449	<1	3.10	28	<0.5	<5	1.12	4	102	1262	40	6.78	0.11	20.73	1048	<2	0.07	1528	301	3	43	0.16	101	<10	51
46450	<1	0.16	<10	<0.5	<5	1.65	4	113	2075	1	5.97	0.01	23.94	1085	2	0.03	1991	<10	<2	52	<0.01	13	<10	48
46451	<1	0.19	<10	<0.5	<5	2.37	4	100	1925	1	5.06	0.01	23.84	918	2	0.03	1799	<10	<2	46	<0.01	13	<10	40
46452	<1	0.14	11	<0.5	<5	2.00	4	116	1779	4	5.72	0.01	23.08	1001	<2	0.03	2047	12	<2	31	<0.01	13	<10	37
46453	<1	0.12	<10	<0.5	<5	1.86	4	109	1605	1	5.59	0.01	24.31	895	<2	0.02	1815	<10	<2	66	<0.01	10	<10	36
46454	<1	0.14	24	<0.5	<5	2.03	4	104	2103	4	5.84	0.01	24.76	914	2	0.03	1790	<10	<2	550	<0.01	11	<10	42
46455	<1	0.15	<10	<0.5	<5	1.28	4	111	2159	1	5.96	0.01	25.71	842	<2	0.03	1974	<10	<2	93	<0.01	13	<10	44
46456	<1	0.17	<10	<0.5	<5	1.25	4	103	2178	2	5.38	0.01	25.03	815	2	0.03	1837	<10	<2	91	<0.01	10	<10	49
46457	<1	0.27	<10	<0.5	<5	1.12	4	97	1765	2	5.39	0.01	23.45	819	<2	0.03	1763	<10	<2	58	0.01	14	<10	45
46458	<1	1.60	62	<0.5	<5	0.64	4	97	1272	75	6.21	0.06	19.68	1016	<2	0.04	1612	199	8	123	0.08	57	<10	70
46459	<1	0.13	<10	<0.5	<5	0.53	3	97	2078	3	4.74	0.01	23.36	1007	<2	0.01	1807	<10	<2	49	<0.01	7	<10	66
46460	<1	0.12	<10	<0.5	<5	0.15	4	109	2015	4	5.74	<0.01	24.06	922	<2	0.02	1912	<10	<2	21	<0.01	7	<10	49
46461	<1	0.13	<10	<0.5	<5	0.28	4	107	1223	3	5.75	0.01	25.18	850	<2	0.03	1937	<10	<2	23	<0.01	10	<10	41
46462	<1	0.13	<10	<0.5	<5	0.32	4	107	997	4	5.79	0.01	24.44	890	<2	0.03	1929	<10	<2	19	<0.01	12	<10	40
46463	<1	0.18	10	<0.5	<5	0.31	4	110	887	4	5.97	0.01	24.16	955	<2	0.02	2022	57	5	23	<0.01	10	<10	55
46464	<1	0.08	<10	<0.5	<5	0.26	4	113	866	3	5.53	<0.01	24.48	868	<2	0.02	2112	<10	<2	28	<0.01	6	<10	39

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V3599RR

Date : Jan-06-09

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type: Core

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
46465	<1	0.08	<10	<0.5	<5	0.21	4	110	1227	4	5.20	0.01	25.15	925	<2	0.02	2004	<10	<2	17	<0.01	6	<10	44
46466	<1	0.11	<10	<0.5	<5	0.29	4	105	1524	3	5.71	<0.01	23.72	902	<2	0.02	1841	<10	<2	23	<0.01	8	<10	47
46467	<1	0.25	<10	<0.5	<5	0.64	4	96	1173	9	5.12	0.01	23.10	1025	<2	0.02	1723	81	36	72	0.02	11	<10	62
46468	<1	0.12	<10	<0.5	<5	0.41	4	105	1226	4	5.59	<0.01	24.01	842	<2	0.02	1943	<10	<2	45	0.01	9	<10	48
46469	<1	0.08	<10	<0.5	<5	0.22	4	109	1464	4	5.73	<0.01	25.17	806	<2	0.02	2032	<10	<2	12	<0.01	7	<10	44
46470	<1	0.14	<10	<0.5	<5	0.31	4	114	1822	5	6.14	<0.01	25.38	881	<2	0.02	1985	<10	<2	17	<0.01	9	<10	45
46471	<1	0.16	<10	<0.5	<5	0.28	5	116	1643	7	6.09	0.01	24.44	913	<2	0.02	1869	<10	<2	4	<0.01	10	<10	36
46472	<1	0.15	<10	<0.5	<5	0.18	5	117	1310	6	6.04	0.01	24.48	922	<2	0.02	1958	<10	<2	7	<0.01	12	<10	34
46473	<1	0.13	<10	<0.5	<5	0.37	4	110	1006	4	5.77	0.01	23.51	943	<2	0.02	1879	<10	<2	22	<0.01	11	<10	35
46474	<1	0.11	<10	<0.5	<5	0.20	4	116	623	5	5.56	<0.01	25.19	929	<2	0.01	2041	<10	<2	18	<0.01	10	<10	29
46475	<1	0.14	<10	<0.5	<5	0.36	4	106	1194	3	5.47	0.01	22.65	919	<2	0.02	1836	<10	<2	13	<0.01	11	<10	32
46476	<1	8.03	2450	4.6	<5	4.81	3	54	116	29	7.66	2.39	5.77	1191	2	2.02	90	5499	36	1684	0.86	192	<10	70
46477	<1	0.55	21	<0.5	<5	0.74	4	108	1645	5	5.75	0.02	21.74	1072	<2	0.03	1728	98	<2	32	0.02	21	<10	70
46478	<1	0.19	28	<0.5	<5	0.47	4	115	899	3	5.58	0.02	23.69	1107	<2	0.03	1988	54	<2	19	0.01	13	<10	42
46479	<1	0.13	<10	<0.5	<5	0.40	4	107	1034	4	5.32	0.01	24.15	1007	<2	0.01	1936	<10	<2	8	<0.01	11	<10	43
46480	<1	0.14	<10	<0.5	<5	0.41	5	124	1304	7	6.22	0.01	24.41	1056	<2	0.01	1893	<10	<2	24	<0.01	12	<10	48
46481	<1	0.09	<10	<0.5	<5	0.19	5	116	1374	6	6.41	0.01	23.70	1031	<2	0.01	1919	<10	<2	26	<0.01	9	<10	48
46482	<1	0.11	<10	<0.5	<5	0.23	5	111	999	5	5.97	0.01	23.69	924	<2	0.02	1907	<10	<2	55	<0.01	10	<10	37
46483	<1	0.14	<10	<0.5	<5	0.16	4	114	851	4	5.55	0.01	24.06	957	<2	0.02	2000	<10	<2	28	<0.01	12	<10	40
46484	<1	0.23	<10	<0.5	<5	0.35	5	104	1119	5	5.35	0.01	23.18	921	<2	0.03	1860	<10	<2	38	<0.01	17	<10	65
46485	<1	0.23	<10	<0.5	<5	0.45	4	98	1353	10	5.14	0.01	21.66	934	<2	0.03	1739	<10	<2	51	<0.01	16	<10	51
46486	5	0.19	<10	<0.5	12	0.43	21	94	1210	29	5.19	0.01	19.27	896	<2	0.03	1633	<10	650	34	<0.01	15	45	2855
46487	1	0.16	<10	<0.5	<5	0.94	9	93	989	13	5.58	0.01	19.65	1085	<2	0.03	1672	10	107	71	<0.01	14	13	791
46488	2	0.10	<10	<0.5	<5	1.56	8	78	704	8	4.28	0.01	18.06	1148	<2	0.03	1451	11	167	112	<0.01	11	12	801
46489	<1	0.11	<10	<0.5	<5	0.90	5	112	1767	4	5.96	0.01	23.53	1133	<2	0.02	1845	<10	2	63	<0.01	10	<10	127
46490	<1	0.14	<10	<0.5	<5	0.37	4	118	2174	3	5.70	0.01	24.80	1176	<2	0.02	1962	<10	<2	34	<0.01	11	<10	54
46491	<1	0.13	<10	<0.5	<5	0.31	4	115	2631	3	5.81	0.01	23.94	1180	<2	0.02	1898	<10	<2	21	<0.01	8	<10	51
46492	<1	0.12	<10	<0.5	<5	0.61	4	103	1430	2	5.24	0.01	22.29	1109	<2	0.02	1877	<10	<2	38	<0.01	10	<10	51
46493	<1	0.13	<10	<0.5	<5	0.25	5	100	1666	5	5.81	0.01	24.05	765	<2	0.03	2009	<10	3	6	<0.01	11	<10	37
46494	<1	0.16	<10	<0.5	<5	0.26	5	107	1279	6	5.01	0.01	23.42	706	<2	0.03	2076	<10	8	18	<0.01	14	<10	32

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V3599RR

Date : Jan-06-09

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type: Core

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
46495	<1	0.10	<10	<0.5	<5	0.38	5	114	1120	4	5.83	0.01	24.84	805	<2	0.03	2242	11	5	12	<0.01	11	<10	28
46496	<1	0.14	23	<0.5	<5	0.39	5	105	1853	3	5.88	0.01	23.40	1253	<2	0.03	2165	<10	7	26	<0.01	17	<10	60
46497	<1	0.13	<10	<0.5	<5	0.45	5	105	1429	1	5.92	0.01	24.30	974	<2	0.04	1979	<10	2	24	<0.01	14	<10	51
46498	<1	0.16	<10	<0.5	<5	0.45	5	111	1324	1	6.01	0.01	25.13	894	<2	0.04	2384	<10	<2	38	<0.01	17	<10	45
46499	<1	0.11	<10	<0.5	<5	0.58	6	113	1186	1	6.39	0.01	25.77	888	<2	0.03	2315	<10	25	41	<0.01	12	<10	43
46500	<1	0.18	<10	<0.5	<5	0.66	5	113	1362	3	5.95	0.01	25.71	1003	<2	0.04	2182	<10	91	40	<0.01	18	<10	50
46413	<1	0.09	<10	<0.5	<5	0.14	4	110	1171	3	5.86	0.01	26.24	863	<2	0.02	2087	<10	<2	8	<0.01	7	<10	37
46414	<1	0.14	<10	<0.5	<5	0.27	4	108	1693	3	5.58	0.01	24.69	1013	<2	0.03	1891	<10	<2	13	<0.01	7	<10	47
46421	<1	0.13	<10	<0.5	<5	0.31	4	105	1539	2	5.53	<0.01	25.20	803	<2	0.02	1947	<10	<2	10	<0.01	10	<10	41
46422	<1	0.16	<10	<0.5	<5	0.13	4	103	1252	1	5.29	<0.01	24.54	762	<2	0.02	1877	<10	<2	5	<0.01	11	<10	38
Duplicates:																								
46401	<1	0.06	<10	<0.5	<5	0.08	2	105	1294	3	5.68	0.02	25.95	854	<2	0.02	2070	10	5	5	<0.01	21	<10	19
46410	<1	0.06	<10	<0.5	<5	0.15	2	106	1080	1	5.62	0.01	25.87	841	<2	0.02	2139	12	15	7	<0.01	23	<10	25
46424	<1	0.10	<10	<0.5	<5	0.28	2	111	1402	<1	6.20	0.01	23.69	871	<2	0.02	2147	<10	7	10	<0.01	28	<10	30
46427	<1	0.16	<10	<0.5	<5	0.60	5	103	1260	3	5.34	0.01	24.41	895	<2	0.03	2366	<10	8	34	<0.01	13	<10	42
46436	<1	0.14	<10	<0.5	<5	1.06	6	109	1407	<1	5.64	0.01	27.43	851	2	0.03	2091	<10	<2	20	<0.01	14	<10	37
46446	<1	0.14	<10	<0.5	<5	1.29	5	100	2054	1	5.79	0.01	26.01	878	<2	0.03	1946	<10	<2	19	<0.01	12	<10	43
46449	<1	3.22	27	<0.5	<5	1.08	4	100	1409	36	6.54	0.11	19.98	1034	<2	0.07	1506	280	<2	45	0.16	100	<10	50
46458	<1	1.66	64	<0.5	<5	0.63	4	99	1265	80	6.23	0.06	20.02	1024	<2	0.05	1649	203	11	120	0.08	59	<10	70
46468	<1	0.11	<10	<0.5	<5	0.38	4	103	1118	4	5.41	<0.01	23.06	815	<2	0.02	1898	<10	<2	42	<0.01	9	<10	47
46471	<1	0.15	<10	<0.5	<5	0.25	4	113	1699	6	5.79	0.01	23.40	881	<2	0.02	1802	<10	<2	3	<0.01	9	<10	35
46480	<1	0.14	<10	<0.5	<5	0.35	5	119	1477	7	5.96	0.01	23.02	1030	<2	0.02	1830	<10	<2	24	<0.01	12	<10	46
46490	<1	0.14	<10	<0.5	<5	0.37	4	118	2115	3	5.81	0.01	25.45	1178	<2	0.02	1962	<10	<2	31	<0.01	11	<10	52
46493	<1	0.14	<10	<0.5	<5	0.25	5	114	1719	5	5.95	0.01	24.68	768	<2	0.03	2094	<10	<2	6	<0.01	11	<10	42
46413	<1	0.09	<10	<0.5	<5	0.14	4	113	1009	2	5.68	0.01	26.32	850	2	0.02	2070	<10	<2	8	<0.01	6	12	36
Standards:																								
Blank	<1	<0.01	<10	<0.5	<5	<0.01	<1	<1	<1	<1	<0.01	<0.01	<0.01	<5	<2	<0.01	<1	<10	<2	<1	<0.01	<1	<10	<2
CH-4	2	8.12	501	1.3	<5	1.94	3	33	127	2096	5.54	1.87	1.43	466	2	3.46	54	733	14	204	0.34	100	<10	215

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V3622RR

Date : Nov-05-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type: Core

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
46501	<1	0.19	16	<0.5	<5	0.75	4	116	1413	3	5.81	0.02	25.81	1057	<2	0.02	2102	<10	8	45	<0.01	17	<10	60
46502	<1	0.15	35	<0.5	<5	0.87	5	118	1244	2	5.93	0.02	26.39	1120	<2	0.02	2222	<10	31	40	<0.01	15	<10	79
46503	<1	0.19	43	<0.5	<5	0.66	4	102	1164	10	4.60	0.02	19.09	685	<2	0.03	1881	61	13	17	<0.01	15	<10	54
46504	<1	0.23	23	<0.5	<5	0.60	4	111	1495	4	5.60	0.01	22.11	661	<2	0.04	2084	<10	3	27	<0.01	17	<10	62
46505	<1	0.43	22	<0.5	<5	0.53	4	115	1352	6	5.67	0.03	23.45	904	<2	0.02	2068	65	12	9	0.01	22	<10	65
46506	<1	1.63	358	1.0	<5	1.80	4	107	899	17	5.75	0.72	20.63	1031	<2	0.38	1743	812	14	202	0.16	54	<10	70
46507	<1	6.70	1590	4.3	<5	4.84	3	66	411	17	6.35	3.28	8.90	1205	<2	1.41	361	2991	47	851	0.59	172	<10	92
46508	<1	0.34	46	<0.5	<5	0.96	4	113	1300	1	5.75	0.11	24.91	1013	<2	0.05	2025	106	6	65	0.02	19	<10	74
46509	<1	0.27	75	<0.5	<5	0.67	4	117	1541	1	5.88	0.10	27.09	1059	<2	0.07	2125	70	4	51	0.02	16	<10	76
46510	<1	0.13	12	<0.5	<5	0.21	4	121	1103	<1	5.97	0.04	27.35	1029	<2	0.02	2250	<10	5	12	<0.01	11	<10	63
46511	<1	0.04	10	<0.5	<5	0.15	5	125	342	1	6.27	0.02	28.92	926	<2	0.02	2280	<10	<2	6	<0.01	9	<10	55
46512	<1	0.09	10	<0.5	<5	0.15	4	123	989	1	5.81	0.02	28.17	939	<2	0.02	2236	<10	6	22	<0.01	9	<10	56
46513	<1	0.08	<10	<0.5	<5	0.16	5	126	699	3	5.95	0.01	28.39	928	<2	0.02	2307	<10	2	13	<0.01	10	<10	51
46514	<1	0.07	<10	<0.5	<5	0.26	5	122	999	1	5.94	0.01	29.00	1223	<2	0.01	2165	<10	6	30	<0.01	7	<10	56
46515	<1	0.10	<10	<0.5	<5	0.19	5	125	1365	<1	6.34	0.01	29.07	1036	<2	0.02	2292	<10	14	13	<0.01	8	<10	62
46516	<1	0.06	<10	<0.5	<5	0.11	4	118	724	1	5.48	0.01	30.05	860	<2	0.01	2536	<10	3	13	<0.01	6	<10	46
46517	<1	0.09	<10	<0.5	<5	0.11	4	127	1358	<1	6.07	0.01	30.01	900	<2	0.02	2486	<10	5	15	<0.01	8	<10	52
46518	<1	0.11	<10	<0.5	<5	0.11	5	123	1261	<1	6.27	0.01	28.69	880	<2	0.02	2304	<10	4	7	<0.01	11	<10	48
46519	<1	0.09	<10	<0.5	<5	0.03	4	113	1147	1	5.49	<0.01	26.68	911	<2	0.01	2148	<10	2	4	<0.01	8	<10	43
46520	<1	0.09	<10	<0.5	<5	0.04	4	110	1446	<1	5.59	0.01	26.88	908	<2	0.01	2011	<10	<2	4	<0.01	8	<10	42
46521	<1	0.10	<10	<0.5	<5	0.02	4	116	999	<1	5.73	0.01	26.30	933	<2	0.01	2212	<10	<2	3	<0.01	11	<10	41
46522	<1	0.12	<10	<0.5	<5	0.09	4	119	1700	1	5.83	<0.01	26.50	985	<2	0.01	2172	<10	<2	11	<0.01	11	<10	50
46523	<1	0.08	<10	<0.5	<5	0.09	2	112	1243	<1	5.72	<0.01	27.68	897	<2	0.01	2055	<10	14	9	<0.01	22	<10	18
46524	<1	0.06	<10	<0.5	<5	0.47	2	106	953	1	5.41	<0.01	25.95	1149	<2	0.01	1973	10	103	67	<0.01	21	<10	69
46525	<1	0.10	<10	<0.5	<5	0.10	2	112	915	<1	5.77	<0.01	27.27	876	<2	0.01	2059	<10	12	12	<0.01	24	<10	14
46526	<1	0.08	<10	<0.5	<5	0.05	2	112	1063	<1	5.99	<0.01	27.67	913	<2	0.01	2069	<10	13	8	<0.01	24	<10	15
46527	<1	0.09	10	<0.5	<5	0.09	2	116	1086	<1	5.87	0.01	27.58	838	<2	0.01	2056	<10	15	16	<0.01	24	<10	28
46528	<1	0.09	<10	<0.5	<5	0.14	2	115	1396	<1	6.08	<0.01	27.01	806	<2	0.01	2063	<10	14	27	<0.01	25	<10	20
46529	<1	0.10	<10	<0.5	<5	0.47	2	115	1633	2	5.85	<0.01	26.32	965	<2	0.01	2068	<10	16	105	<0.01	22	<10	40
46530	<1	0.10	<10	<0.5	<5	0.76	2	113	1709	4	6.06	<0.01	25.51	976	<2	0.02	2033	17	23	221	<0.01	25	<10	41

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

ICP-AES Report																								
Multi-Acid Digestion																								
Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
46531	<1	0.15	<10	<0.5	<5	1.34	3	115	1525	5	6.30	0.01	25.54	1043	<2	0.02	2137	12	30	208	<0.01	26	<10	59
46532	2	7.62	2348	13.0	<5	1.40	6	29	135	22	4.63	3.96	6.63	2660	<2	1.53	103	2750	924	733	0.40	116	39	2095
46533	1	8.06	2231	16.1	<5	2.60	1	27	127	13	4.36	3.92	2.89	1381	<2	2.78	82	2654	151	1064	0.42	114	<10	136
46534	1	8.22	2282	16.6	<5	3.24	1	27	123	5	4.46	4.07	2.22	1420	<2	3.14	41	2658	252	1210	0.45	117	<10	193
46535	1	7.00	1768	13.8	<5	3.11	<1	22	113	6	3.84	3.32	1.93	1202	<2	2.77	37	2490	37	942	0.35	97	<10	93
46536	1	8.17	2372	14.6	<5	2.86	3	25	125	6	4.74	4.47	2.18	2464	<2	2.72	37	2891	522	983	0.39	114	12	576
46537	1	8.13	2080	17.9	6	3.41	<1	27	114	7	4.46	3.82	2.12	963	<2	3.58	40	2798	46	1292	0.47	116	<10	115
46538	1	8.33	2127	18.8	<5	3.44	<1	28	129	9	4.47	3.82	2.23	895	<2	3.57	48	2759	35	1392	0.50	119	<10	92
46539	1	8.70	2087	16.6	<5	3.30	<1	25	116	9	4.04	3.66	2.01	841	3	3.40	33	2656	22	1402	0.49	115	<10	70
46540	<1	8.34	2131	16.9	7	3.25	<1	26	130	14	4.11	3.73	2.01	856	3	3.42	35	2766	27	1382	0.50	118	<10	75
46541	1	8.77	2086	16.4	10	3.24	<1	25	116	6	4.06	3.64	2.01	907	2	3.45	36	2767	27	1298	0.48	115	<10	91
46542	1	8.45	2022	15.9	8	3.73	<1	26	123	6	4.04	3.66	1.97	986	<2	3.32	33	2675	40	1164	0.47	114	<10	98
46543	1	8.12	1941	15.6	7	3.53	1	25	112	3	4.08	3.92	1.97	1806	<2	2.98	34	2527	96	988	0.42	108	<10	171
46544	1	8.32	2302	15.6	<5	3.45	1	26	156	8	4.34	5.00	2.08	2294	<2	2.44	35	2697	97	1026	0.45	115	10	232
46545	1	8.74	2077	6.0	<5	3.11	<1	26	135	13	4.18	4.44	2.16	1186	2	2.91	35	2755	73	1057	0.50	106	<10	77
46546	1	8.09	2279	3.8	<5	3.06	<1	26	147	5	4.40	6.58	2.97	2292	2	1.42	90	2736	84	893	0.34	98	10	133
46547	1	8.39	2757	2.8	<5	2.82	1	21	108	1	4.59	8.10	2.51	3670	5	0.81	37	3019	140	892	0.26	98	12	328
46548	1	1.88	463	0.7	<5	1.15	4	94	1273	2	6.41	0.92	21.48	3104	7	0.06	1722	574	38	121	0.09	26	<10	190
46549	<1	1.75	104	0.5	<5	2.16	6	111	1145	7	6.33	0.28	21.32	2158	4	0.04	1773	726	355	148	0.14	49	<10	420
46550	3	0.36	32	<0.5	<5	3.66	14	93	1386	23	6.33	0.05	18.16	2437	2	0.03	1623	108	914	164	0.02	17	30	2070
46551	<1	0.18	15	<0.5	<5	1.02	4	117	1537	1	5.85	0.02	25.43	977	2	0.02	2220	18	19	73	0.01	14	<10	88
46552	<1	0.14	13	<0.5	<5	0.50	4	114	1346	2	5.72	0.02	26.76	1056	<2	0.02	2228	<10	23	11	0.01	11	<10	101
46553	<1	0.14	<10	<0.5	<5	0.60	4	111	1541	<1	5.61	0.01	26.29	922	2	0.02	1859	<10	5	37	<0.01	12	<10	55
46554	<1	0.12	<10	<0.5	<5	0.90	4	112	1322	<1	5.66	0.01	25.66	873	2	0.02	2022	<10	7	83	<0.01	11	<10	50
46555	<1	0.14	15	<0.5	<5	0.43	4	107	1209	12	5.47	0.01	25.32	941	2	0.02	2080	<10	32	33	<0.01	12	<10	129
46556	<1	0.10	<10	<0.5	<5	0.43	4	112	1450	1	5.34	0.01	25.93	858	<2	0.01	2102	<10	<2	22	<0.01	9	<10	46
46557	<1	0.11	10	<0.5	<5	0.23	4	116	1571	1	5.34	0.01	26.00	961	2	0.02	2078	<10	6	14	0.01	7	<10	50
46558	<1	0.09	<10	<0.5	<5	0.23	4	123	1306	<1	5.67	0.01	27.07	1005	<2	0.01	2287	<10	2	14	<0.01	8	<10	44
46559	<1	0.09	<10	<0.5	<5	0.12	4	119	1332	<1	5.65	0.01	27.46	918	<2	0.01	2242	<10	<2	7	<0.01	9	<10	44
46560	<1	0.11	<10	<0.5	<5	0.16	4	113	1275	<1	5.59	0.01	27.92	848	<2	0.02	2136	<10	<2	6	<0.01	11	<10	43

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V3622RR

Date : Nov-05-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type: Core

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
46561	<1	0.13	<10	<0.5	<5	0.10	4	115	1312	<1	5.81	0.01	27.08	809	<2	0.02	2174	<10	<2	4	<0.01	13	<10	44
46562	<1	0.15	<10	<0.5	<5	0.37	4	105	1172	<1	5.55	0.01	27.00	807	<2	0.01	2037	<10	<2	12	<0.01	14	<10	43
46563	<1	0.13	<10	<0.5	<5	0.17	4	111	1668	<1	5.81	0.01	27.43	829	<2	0.02	2127	<10	<2	7	<0.01	12	<10	45
46564	<1	0.13	<10	<0.5	<5	0.21	4	114	1712	<1	6.28	0.01	25.87	812	<2	0.02	2152	<10	<2	6	<0.01	12	<10	47
46565	<1	0.11	<10	<0.5	<5	0.14	4	112	2092	1	5.71	0.01	26.71	844	<2	0.01	2290	<10	<2	7	<0.01	8	<10	45
46566	<1	0.10	<10	<0.5	<5	0.10	4	115	1411	<1	5.47	0.01	28.06	852	<2	0.01	2326	<10	2	5	<0.01	8	<10	40
46567	<1	0.07	<10	<0.5	<5	0.10	2	108	2260	<1	5.62	0.01	27.43	863	<2	0.03	2422	<10	13	6	<0.01	20	<10	29
46568	<1	0.07	<10	<0.5	<5	0.14	2	118	2386	<1	5.55	0.02	27.89	915	<2	0.03	2428	<10	16	7	<0.01	19	<10	28
46569	<1	0.05	<10	<0.5	<5	0.18	2	114	1728	<1	5.50	0.02	28.25	926	<2	0.03	2338	<10	18	8	<0.01	20	<10	24
46570	<1	0.04	<10	<0.5	<5	0.19	2	112	1612	<1	5.78	0.02	26.93	849	<2	0.03	2373	<10	15	18	<0.01	21	<10	18
46571	<1	4.08	1629	13.3	22	4.62	2	65	743	<1	5.55	2.06	13.87	1085	<2	0.75	794	2752	54	897	0.43	132	<10	79
46572	<1	6.54	2936	21.6	31	5.13	2	52	407	<1	6.26	3.77	6.59	980	<2	1.85	185	4340	17	1288	0.69	193	<10	54
46573	<1	6.55	2741	21.4	33	5.29	2	59	412	6	6.66	3.29	8.03	1789	<2	1.64	159	4910	30	1044	0.72	209	<10	100
46574	<1	3.31	818	7.9	13	3.07	2	72	698	15	5.55	1.42	13.65	900	2	0.86	1143	1281	25	465	0.28	106	<10	52
46575	1	0.21	64	0.5	<5	0.20	3	117	1341	13	6.31	0.10	23.51	790	<2	0.06	2262	120	21	23	0.02	34	<10	23
46576	<1	0.22	71	0.6	<5	0.28	2	116	1206	4	5.84	0.11	25.02	821	<2	0.07	2282	143	14	30	0.02	29	<10	11
46577	<1	0.08	13	<0.5	<5	0.75	2	113	1795	3	5.57	0.03	25.57	905	<2	0.03	1917	14	18	92	<0.01	23	<10	24
46578	1	0.07	17	<0.5	<5	0.34	3	116	1438	3	5.71	0.03	25.31	720	<2	0.03	2128	22	25	30	<0.01	24	<10	22
46579	<1	7.02	1171	20.2	31	5.23	4	73	604	23	8.03	2.03	9.97	6728	<2	0.82	389	3336	248	546	0.67	220	13	483
46580	<1	0.27	54	0.7	<5	0.60	3	117	1465	5	5.98	0.09	25.92	1087	<2	0.06	2089	124	64	55	0.03	31	<10	55
46581	<1	0.13	18	<0.5	<5	0.28	2	116	1103	6	5.13	0.04	26.75	871	<2	0.04	2119	30	22	25	0.01	25	<10	22
46582	<1	0.06	<10	<0.5	<5	0.24	2	123	1591	6	5.60	0.02	26.65	842	<2	0.03	2148	<10	21	21	<0.01	22	<10	13
46583	<1	0.39	63	0.8	<5	0.40	2	118	1920	5	6.04	0.12	26.08	1088	<2	0.07	2056	170	29	40	0.04	35	<10	37
46584	<1	0.17	17	<0.5	<5	0.30	2	119	1686	4	5.95	0.05	26.49	963	<2	0.04	2081	68	21	21	0.01	28	<10	24
46585	<1	0.09	<10	<0.5	<5	0.79	2	115	1640	4	5.62	0.03	25.48	1216	<2	0.03	2018	<10	20	55	<0.01	25	<10	29
46586	<1	0.06	<10	<0.5	<5	0.42	2	114	1687	6	5.73	0.03	25.96	1032	<2	0.03	2074	10	19	44	<0.01	23	<10	25
46587	<1	0.05	<10	<0.5	<5	0.55	2	117	1407	54	5.42	0.02	25.59	844	<2	0.02	2077	<10	17	25	<0.01	23	<10	24
46588	1	0.07	<10	<0.5	<5	0.12	2	130	1309	531	5.55	0.02	26.22	714	<2	0.03	2130	<10	16	4	<0.01	25	<10	16
46589	1	0.07	<10	<0.5	7	0.07	4	151	1035	170	5.91	0.01	22.49	700	<2	0.01	2139	14	13	5	<0.01	10	<10	15
46590	<1	0.07	<10	<0.5	9	0.09	5	116	1583	8	6.47	0.01	23.67	928	<2	0.01	2144	<10	7	3	<0.01	10	<10	18

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V3622RR

Date : Nov-05-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type: Core

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
46591	<1	0.12	12	<0.5	<5	0.12	4	117	1540	1	6.21	<0.01	24.65	935	<2	0.01	2101	<10	2	16	<0.01	10	<10	65
46592	<1	0.11	<10	<0.5	<5	0.25	4	128	2200	4	5.41	<0.01	25.99	961	2	0.01	2478	<10	2	9	<0.01	7	<10	80
46593	<1	0.10	<10	<0.5	<5	0.04	3	108	1231	6	6.00	0.01	25.76	725	<2	0.02	2071	<10	4	1	<0.01	11	<10	35
46594	<1	0.15	11	<0.5	<5	0.10	5	123	1255	12	6.40	<0.01	25.59	830	<2	0.02	2181	<10	2	2	<0.01	16	<10	49
46595	<1	0.15	10	<0.5	<5	0.09	5	120	1690	10	6.50	0.01	24.83	824	2	0.02	2030	<10	<2	2	<0.01	14	<10	49
46596	<1	0.14	10	<0.5	<5	0.07	5	122	1484	10	6.31	<0.01	25.01	823	2	0.02	2131	<10	3	2	<0.01	14	<10	46
46597	<1	0.14	<10	<0.5	<5	0.11	5	117	1594	10	6.38	<0.01	24.66	870	<2	0.01	2014	<10	<2	1	0.01	14	<10	48
46598	<1	0.12	<10	<0.5	<5	0.11	5	123	2129	11	6.55	<0.01	24.91	977	<2	0.01	2202	<10	10	2	<0.01	8	<10	52
46599	<1	0.10	<10	<0.5	<5	0.13	4	121	1702	8	5.70	<0.01	24.76	938	<2	0.01	2160	<10	<2	8	<0.01	7	<10	49
46600	<1	0.12	<10	<0.5	<5	0.09	4	115	1980	7	5.93	<0.01	25.32	930	<2	0.01	2062	<10	<2	3	<0.01	8	<10	49
Duplicates:																								
46501	<1	0.18	15	<0.5	<5	0.73	4	116	1529	2	5.83	0.02	26.25	1056	<2	0.02	2112	<10	5	42	<0.01	17	<10	61
46510	<1	0.12	18	<0.5	<5	0.20	5	127	1360	<1	6.28	0.05	29.14	1052	<2	0.02	2329	<10	5	12	<0.01	10	<10	67
46520	<1	0.09	<10	<0.5	<5	0.04	4	111	1485	<1	5.76	0.01	27.29	925	<2	0.01	2061	<10	<2	4	<0.01	8	<10	44
46523	<1	0.08	<10	<0.5	<5	0.09	2	106	1390	<1	5.83	<0.01	27.65	898	<2	0.01	2081	<10	12	9	<0.01	22	<10	18
46532	2	8.35	2338	12.8	<5	1.42	6	27	124	22	4.89	3.86	6.71	2675	<2	1.61	97	2559	889	723	0.40	114	39	2161
46542	1	8.44	2009	15.5	7	3.76	<1	24	117	7	3.91	3.58	1.95	973	<2	3.36	30	2706	38	1163	0.45	110	<10	96
46545	1	8.09	1986	5.8	<5	3.07	<1	26	133	13	4.13	4.31	2.12	1136	2	2.81	35	2623	67	978	0.45	103	<10	78
46554	<1	0.12	<10	<0.5	<5	0.93	4	108	1308	<1	5.72	0.01	25.95	868	<2	0.02	1980	<10	6	81	<0.01	11	<10	49
46564	<1	0.13	<10	<0.5	<5	0.21	5	116	1530	<1	6.46	0.01	27.19	825	<2	0.02	2219	<10	<2	6	<0.01	12	<10	45
46567	1	0.07	<10	<0.5	<5	0.10	2	116	2332	1	5.67	0.02	27.60	883	<2	0.03	2430	<10	14	6	<0.01	20	<10	25
46576	<1	0.21	68	0.5	<5	0.25	2	117	1198	3	5.76	0.10	24.68	820	<2	0.06	2309	135	14	30	0.02	29	<10	11
46586	<1	0.06	<10	<0.5	<5	0.41	2	110	1530	7	5.63	0.02	25.85	1030	<2	0.03	2082	<10	16	42	<0.01	22	<10	23
46589	<1	0.07	<10	<0.5	7	0.07	4	153	999	184	5.84	0.01	22.44	703	<2	0.01	2138	21	11	5	<0.01	9	<10	12
46598	1	0.12	<10	<0.5	<5	0.11	5	122	2333	11	6.60	<0.01	25.32	982	<2	0.01	2214	<10	18	3	0.01	8	<10	52
Standards:																								
Blank	<1	<0.01	<10	<0.5	<5	<0.01	<1	1	2	<1	0.01	<0.01	0.01	<5	<2	0.01	<1	<10	<2	<1	<0.01	<1	<10	<2
CH-4	2	8.32	502	1.7	<5	2.05	3	38	139	2055	6.07	1.97	1.61	521	3	3.42	55	719	15	205	0.36	102	10	229

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V3723RR

Date : Nov-06-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type: Drill Core

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
46601	1	0.11	23	<0.5	<5	0.13	2	116	2069	21	6.28	0.03	26.04	914	<2	0.04	1971	14	78	9	0.01	26	<10	43
46602	<1	0.08	<10	<0.5	<5	0.33	4	121	1023	6	6.77	0.01	25.42	1036	<2	0.02	2379	<10	39	13	<0.01	9	<10	45
46603	1	0.10	<10	<0.5	<5	0.20	2	129	2076	6	6.39	0.01	24.30	1135	<2	0.02	2101	<10	31	12	<0.01	32	<10	34
46604	1	0.10	<10	<0.5	<5	0.05	2	109	1369	7	6.20	0.01	25.42	810	<2	0.02	2128	<10	19	3	<0.01	33	<10	18
46605	<1	0.09	<10	<0.5	<5	0.20	2	120	1379	10	6.56	<0.01	25.03	864	<2	0.02	2201	<10	19	5	<0.01	33	<10	15
46606	1	0.11	<10	<0.5	<5	0.04	2	118	1171	8	5.91	0.01	25.09	752	<2	0.02	2230	<10	15	2	<0.01	34	<10	15
46607	<1	0.11	<10	<0.5	<5	0.17	2	115	1103	11	5.85	0.01	26.07	809	<2	0.02	2145	<10	19	2	<0.01	31	<10	13
46608	<1	0.09	<10	<0.5	<5	0.08	2	115	1124	10	5.82	<0.01	24.98	739	<2	0.02	2159	<10	18	2	<0.01	30	<10	11
46609	<1	0.05	<10	<0.5	<5	0.28	2	120	1047	11	5.72	0.01	24.36	732	<2	0.02	2222	15	19	12	<0.01	27	<10	11
46610	<1	0.07	<10	<0.5	<5	0.25	2	113	1033	10	5.75	0.01	24.07	694	<2	0.02	2074	<10	14	12	<0.01	29	<10	8
46611	<1	0.06	<10	<0.5	<5	1.02	2	117	1159	7	5.71	0.01	23.29	809	<2	0.02	2122	<10	18	143	<0.01	27	<10	23
46612	<1	0.09	<10	<0.5	<5	0.77	2	114	1307	5	5.67	0.01	23.79	817	<2	0.02	2037	<10	21	29	<0.01	27	<10	30
46613	<1	0.05	<10	<0.5	<5	0.12	3	117	891	4	6.14	0.01	24.30	694	<2	0.02	2230	<10	19	6	<0.01	28	<10	20
46614	<1	0.08	<10	<0.5	<5	0.08	2	115	1140	2	5.90	0.01	24.65	714	<2	0.02	2126	<10	16	3	<0.01	29	<10	15
46615	<1	0.10	<10	<0.5	<5	0.11	2	113	1368	2	6.08	0.01	24.28	689	<2	0.02	2036	<10	14	3	<0.01	33	<10	13
46616	<1	0.09	<10	<0.5	<5	0.01	2	111	1177	3	5.74	0.01	24.56	673	<2	0.02	2012	<10	15	1	<0.01	29	<10	11
46617	<1	0.07	<10	<0.5	<5	0.03	2	112	1248	4	5.80	0.01	24.50	660	<2	0.02	2162	<10	14	2	<0.01	27	<10	12
46618	<1	0.06	<10	<0.5	<5	0.26	2	111	1544	5	5.51	0.01	24.82	765	<2	0.02	2229	<10	13	4	<0.01	24	<10	16
46619	<1	0.09	<10	<0.5	<5	0.84	2	104	1142	2	5.28	0.01	23.83	781	<2	0.02	1889	<10	34	28	<0.01	26	<10	22
46620	<1	0.09	<10	<0.5	<5	0.12	2	112	1275	3	5.78	0.01	24.67	694	<2	0.02	2114	<10	17	3	<0.01	29	<10	11
46621	<1	0.07	<10	<0.5	<5	0.03	2	117	1447	6	5.90	0.01	24.91	720	<2	0.02	2212	11	16	2	<0.01	28	<10	10
46622	<1	0.10	25	<0.5	<5	0.02	2	115	1409	3	5.98	0.01	24.50	719	<2	0.02	2103	<10	16	3	<0.01	31	<10	11
46623	<1	3.63	1060	1.7	<5	3.92	3	83	910	19	6.41	1.36	16.52	1103	2	0.45	1120	2158	20	798	0.28	97	<10	67
46624	<1	3.12	1336	1.7	<5	3.44	4	87	915	53	6.58	1.76	15.30	1081	2	0.35	1064	2345	17	657	0.30	97	<10	78
46625	<1	0.31	65	<0.5	<5	0.20	4	105	1468	3	6.27	0.07	25.68	746	2	0.03	1925	85	2	35	0.01	22	<10	44
46626	<1	0.29	58	<0.5	<5	0.31	4	108	1492	4	5.92	0.06	25.37	719	2	0.02	1980	60	2	24	0.01	23	<10	45
46627	<1	0.20	13	<0.5	<5	0.15	4	106	1458	1	5.77	0.01	26.30	741	2	0.01	1977	<10	2	8	<0.01	20	<10	41
46628	<1	0.14	14	<0.5	<5	0.19	4	111	1667	7	6.13	0.02	26.31	758	2	0.01	2060	<10	2	9	<0.01	13	<10	40
46629	<1	0.13	10	<0.5	<5	0.31	4	109	1253	2	5.60	0.01	26.01	727	<2	0.01	2071	<10	<2	57	<0.01	14	<10	37
46630	<1	0.13	<10	<0.5	<5	0.29	4	119	1654	6	6.27	0.01	26.98	1006	2	0.01	2177	<10	10	29	<0.01	12	<10	55

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type: Drill Core

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V3723RR

Date : Nov-06-08

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
46631	<1	0.12	<10	<0.5	<5	0.69	4	115	1418	3	5.65	0.01	27.33	1082	2	0.01	2099	<10	5	101	<0.01	12	<10	54
46632	3	0.25	12	<0.5	<5	1.22	10	101	1251	221	7.11	0.01	21.75	1513	2	0.02	1870	<10	325	90	<0.01	15	18	1216
46633	1	6.11	586	3.0	<5	1.77	6	57	530	33	9.95	2.49	12.99	4907	<2	1.20	571	2382	177	718	0.41	112	14	568
46634	2	8.49	1602	5.0	<5	3.06	3	31	169	20	4.77	2.85	4.33	1555	2	3.77	121	2795	262	1102	0.46	112	13	663
46635	<1	0.34	90	<0.5	<5	0.19	4	120	1928	2	6.22	0.13	24.82	979	<2	0.09	2140	80	10	61	0.02	11	<10	72
46636	<1	0.23	67	<0.5	<5	0.60	4	112	1536	1	6.35	0.07	23.92	905	<2	0.09	1980	53	10	130	0.01	10	<10	64
46637	<1	0.11	21	<0.5	<5	0.96	3	93	1352	1	4.93	0.02	23.51	1755	<2	0.02	1722	<10	8	104	<0.01	8	<10	91
46638	<1	0.12	17	<0.5	<5	0.18	4	110	1655	<1	5.83	0.01	24.82	959	<2	0.02	2022	<10	7	45	<0.01	9	<10	66
46639	<1	0.12	15	<0.5	<5	0.34	5	122	1699	<1	6.23	0.01	26.52	1011	<2	0.01	2188	<10	3	59	<0.01	10	<10	69
46640	<1	0.11	10	<0.5	<5	0.53	4	111	1421	<1	5.74	0.01	23.66	889	<2	0.01	2121	<10	2	64	<0.01	10	<10	60
46641	<1	0.11	<10	<0.5	<5	0.45	4	105	1549	<1	5.70	0.01	24.46	895	<2	0.01	1920	<10	<2	33	<0.01	10	<10	59
46642	<1	0.11	13	<0.5	<5	0.29	4	109	1346	1	5.44	0.01	25.26	857	<2	0.01	2039	<10	2	25	<0.01	9	<10	58
46643	<1	0.11	17	<0.5	<5	0.24	4	109	1719	<1	5.92	0.01	24.99	901	<2	0.01	1991	<10	5	31	<0.01	9	<10	67
46644	<1	0.10	<10	<0.5	<5	0.08	4	104	1209	<1	5.56	0.01	26.38	836	<2	0.01	2019	<10	5	12	<0.01	9	<10	59
46645	<1	0.07	11	<0.5	8	0.09	4	104	1194	<1	5.85	0.01	26.88	864	<2	0.01	2097	<10	5	16	<0.01	8	<10	30
46646	<1	0.08	<10	<0.5	10	0.32	4	106	1365	<1	6.04	0.01	26.74	938	<2	0.01	1954	<10	3	11	<0.01	8	<10	37
46647	<1	0.06	12	<0.5	8	0.32	4	108	1097	<1	5.73	<0.01	26.53	857	<2	0.01	2172	<10	3	17	<0.01	7	<10	28
46648	<1	0.07	<10	<0.5	7	0.57	4	104	1211	<1	5.89	0.01	25.96	911	<2	0.01	2002	<10	<2	16	<0.01	8	<10	27
46649	<1	0.09	11	<0.5	9	0.47	4	103	1042	3	5.43	0.01	26.09	855	<2	0.01	2002	<10	4	12	<0.01	10	<10	22
46650	<1	0.12	74	<0.5	12	0.83	4	109	1400	<1	5.67	0.01	26.44	866	<2	0.02	2079	<10	3	42	<0.01	12	<10	26
46651	<1	0.09	77	<0.5	6	1.15	4	103	1079	<1	5.35	0.01	25.69	757	<2	0.01	2009	<10	5	67	<0.01	11	<10	18
46652	<1	0.08	49	<0.5	10	0.55	5	114	1400	<1	6.15	0.01	25.99	704	<2	0.01	2140	<10	2	18	<0.01	11	<10	17
46653	<1	0.06	10	<0.5	7	0.12	4	113	775	1	4.67	0.01	25.10	561	<2	0.01	2220	<10	3	10	<0.01	10	<10	9
46654	<1	0.08	63	<0.5	10	0.33	4	109	1224	1	5.37	0.01	25.38	750	<2	0.01	2095	<10	5	9	<0.01	11	<10	13
46655	<1	0.96	71	<0.5	5	0.17	4	101	1334	17	5.95	0.03	25.14	977	<2	0.02	1714	76	2	9	0.05	42	<10	14
46656	<1	0.08	54	<0.5	8	0.02	3	100	1057	3	4.13	0.01	25.83	678	<2	0.01	2010	<10	5	8	<0.01	9	<10	7
46657	<1	0.10	62	<0.5	7	0.02	3	100	1463	2	4.30	0.01	25.07	778	<2	0.02	2105	<10	4	8	<0.01	10	<10	13
46658	<1	8.69	151	1.6	<5	3.35	3	55	283	<1	6.94	0.03	15.38	1405	<2	0.03	227	939	<2	854	0.57	324	<10	42
46659	<1	1.45	36	<0.5	6	0.27	4	124	1445	124	6.22	0.02	23.09	761	37	0.02	2192	151	4	14	0.09	62	<10	18
46660	<1	0.38	60	<0.5	6	0.18	3	103	773	26	4.21	<0.01	25.80	620	<2	0.01	2089	36	3	31	0.02	19	<10	10

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V3723RR

Date : Nov-06-08

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type: Drill Core

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
46661	<1	0.11	<10	<0.5	10	0.06	3	133	1305	22	4.88	<0.01	27.13	721	<2	0.01	2254	<10	2	5	0.01	8	<10	19
46662	<1	0.09	12	<0.5	10	0.07	3	116	1251	84	4.35	<0.01	26.91	688	<2	0.01	2166	<10	<2	5	<0.01	7	<10	18
46663	1	0.08	<10	<0.5	8	0.11	3	104	1393	154	4.43	0.01	26.77	714	<2	0.01	2244	<10	2	3	<0.01	6	<10	20
46664	<1	0.09	<10	<0.5	9	0.03	3	111	1537	29	4.52	0.01	26.58	733	<2	0.01	2274	<10	<2	3	<0.01	6	<10	20
46665	<1	0.08	<10	<0.5	10	0.22	3	115	1282	11	4.35	0.01	27.52	785	<2	0.01	2348	10	4	6	<0.01	6	<10	18
46666	<1	0.07	<10	<0.5	10	0.11	3	107	1235	5	4.28	0.01	26.69	715	<2	0.01	2138	<10	5	6	<0.01	5	<10	21
46667	<1	0.07	<10	<0.5	8	0.20	3	107	1720	4	4.92	0.01	26.78	854	<2	0.01	2333	10	2	9	<0.01	6	<10	37
46668	<1	0.10	<10	<0.5	12	0.31	3	111	2200	8	4.83	0.01	27.82	905	<2	0.01	2432	24	8	28	0.01	6	<10	53
46669	<1	0.08	21	<0.5	9	0.43	3	110	1710	11	4.58	0.01	27.52	920	<2	0.01	2453	<10	10	85	<0.01	6	<10	45
46670	<1	5.05	2836	3.3	<5	5.02	4	72	809	39	6.75	2.58	11.14	2986	<2	0.52	614	3042	327	943	0.57	157	<10	202
46671	<1	0.16	56	<0.5	9	0.55	2	103	1440	17	3.48	0.05	26.74	696	<2	0.02	2337	57	10	107	0.01	7	<10	48
46672	<1	0.20	71	<0.5	7	0.31	2	95	1643	23	3.55	0.07	26.60	783	<2	0.03	2052	84	11	46	0.02	9	<10	51
46673	<1	0.08	<10	<0.5	9	0.12	2	107	1631	7	3.26	0.01	27.14	757	<2	0.02	2252	<10	9	18	<0.01	4	<10	55
46674	<1	0.08	<10	<0.5	7	0.27	2	108	1271	7	3.43	0.01	27.40	829	<2	0.01	2184	29	6	37	<0.01	5	<10	40
46675	<1	0.40	15	<0.5	8	0.87	4	107	1515	11	4.90	0.05	23.88	881	<2	0.03	2000	91	19	128	0.02	19	<10	75
46676	<1	6.79	2019	6.1	<5	3.08	1	31	163	16	4.05	3.77	3.35	836	5	2.88	168	2774	27	1300	0.48	106	<10	64
46677	<1	7.92	1937	5.9	<5	3.10	1	26	122	20	4.06	3.80	2.39	788	<2	2.98	77	2639	29	1276	0.45	102	<10	72
46678	<1	7.82	2087	6.2	<5	3.13	1	25	115	17	4.21	3.92	2.12	842	<2	3.08	42	2879	35	1228	0.49	107	<10	75
46679	<1	7.26	1891	5.7	<5	3.15	1	25	126	21	4.18	3.63	2.35	958	<2	3.02	54	2907	45	1158	0.45	105	<10	95
46680	<1	5.11	1606	3.7	<5	3.32	3	55	571	27	5.45	2.41	8.90	1164	<2	1.90	588	2523	52	796	0.38	106	<10	101
46681	<1	9.20	2286	4.9	<5	2.80	1	23	99	12	4.09	4.73	1.91	810	4	2.73	39	2596	42	1228	0.54	119	<10	65
46682	<1	8.28	2537	4.5	<5	3.37	3	24	105	31	4.15	5.17	1.78	1302	5	2.62	44	2621	226	1204	0.45	116	10	238
46683	<1	8.64	2404	4.9	<5	3.35	2	24	93	23	4.16	5.09	1.63	1228	5	2.76	34	2729	80	1201	0.49	120	<10	126
46684	<1	8.35	2395	4.5	<5	3.58	6	23	91	46	4.27	5.05	1.75	1342	4	2.80	29	2542	877	1240	0.51	117	19	992
46685	<1	8.29	2276	4.9	<5	3.23	2	23	86	31	4.24	4.98	1.64	944	3	2.88	28	2597	35	1235	0.50	117	<10	98
46686	<1	8.06	2460	4.6	<5	3.45	3	25	99	38	4.56	4.90	1.94	1714	4	2.53	39	2904	267	1195	0.48	123	11	467
46687	<1	5.96	2429	3.8	<5	5.76	4	54	389	45	6.32	3.25	6.01	1464	<2	1.43	301	3954	26	1451	0.58	169	<10	138
46688	<1	6.99	2294	3.8	<5	4.88	3	45	281	51	6.07	3.09	4.81	1287	<2	2.04	159	3351	32	1277	0.61	175	<10	139
46689	<1	8.38	2187	21.6	26	5.54	2	48	203	24	6.96	3.41	3.84	1412	<2	2.01	46	2940	28	1306	0.66	225	<10	141
46690	<1	8.16	2343	16.5	16	5.57	4	45	204	21	7.12	3.66	3.88	2646	<2	1.55	65	2856	115	1108	0.49	211	14	502

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

WHY Resources

Attention: Frank Marasco

Project: Record Ridge South

Sample type: Drill Core

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V3723RR

Date : Nov-06-08

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
Duplicates:																								
46601	2	0.09	13	<0.5	<5	0.12	2	116	1971	17	6.29	0.02	25.71	910	<2	0.03	1977	10	71	6	<0.01	26	<10	30
46610	<1	0.07	<10	<0.5	<5	0.25	2	116	1033	11	5.80	0.01	24.97	710	<2	0.02	2158	<10	18	12	<0.01	28	<10	9
46620	<1	0.09	<10	<0.5	<5	0.12	2	108	1305	2	5.74	0.01	24.62	681	<2	0.02	2049	<10	14	3	<0.01	29	<10	13
46623	<1	3.41	1042	1.7	<5	3.80	3	86	852	20	6.33	1.37	16.00	1079	2	0.45	1103	2205	19	791	0.29	95	<10	77
46632	2	0.25	13	<0.5	<5	1.18	10	97	1194	243	7.03	0.02	21.22	1495	2	0.02	1857	<10	316	87	<0.01	15	18	1205
46642	<1	0.11	17	<0.5	<5	0.29	4	107	1432	1	5.45	0.01	24.71	859	<2	0.01	2031	<10	2	25	<0.01	10	<10	62
46645	<1	0.08	<10	<0.5	11	0.09	4	109	1540	<1	5.62	0.01	25.92	851	<2	0.01	2054	<10	3	15	<0.01	9	<10	30
46654	<1	0.09	62	<0.5	7	0.33	4	109	1389	2	5.23	0.01	24.96	749	<2	0.01	2001	<10	5	9	<0.01	11	<10	15
46664	<1	0.09	<10	<0.5	10	0.04	3	110	1517	27	4.45	0.01	26.39	728	2	0.01	2265	<10	3	4	<0.01	6	<10	18
46667	<1	0.08	<10	<0.5	11	0.20	3	110	1861	4	4.90	0.01	26.64	861	<2	0.01	2374	<10	3	9	<0.01	6	<10	40
46676	<1	7.18	2022	6.3	<5	3.19	2	31	159	17	4.17	3.81	3.42	853	4	2.89	166	2781	25	1312	0.49	107	<10	68
46686	<1	8.23	2489	4.5	<5	3.49	3	25	100	38	4.61	4.91	1.94	1737	4	2.55	34	2985	255	1216	0.49	124	12	455
46689	<1	8.71	2167	21.3	25	5.71	2	47	206	25	7.23	3.46	3.95	1461	<2	1.98	47	3002	45	1308	0.66	222	<10	183
Standards:																								
Blank	<1	<0.01	<10	<0.5	<5	<0.01	<1	1	<1	1	<0.01	<0.01	0.01	<5	<2	0.01	<1	<10	<2	<1	<0.01	<1	<10	<2
CH-4	2	7.10	512	1.7	<5	1.94	4	32	129	1938	5.33	1.87	1.43	509	<2	3.38	55	801	17	206	0.35	102	<10	208

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.

Assayers Canada

8282 Sherbrooke St., Vancouver, B.C., V5X 4R6

Tel: (604) 327-3436 Fax: (604) 327-3423

Report No : 8V3790RR

Date : Nov-13-08

WHY Resources

Attention: Frank Maraso

Project: Record Ridge South

Sample type: Drill Core

ICP-AES Report

Multi-Acid Digestion

Sample Number	Ag ppm	Al %	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	K %	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	Sr ppm	Ti %	V ppm	W ppm	Zn ppm
46729	<1	0.58	53	<0.5	<5	1.37	4	103	1148	17	5.42	0.11	23.25	1097	2	0.14	2020	16	7	22	0.03	33	<10	86
46730	<1	0.62	31	<0.5	<5	1.97	3	92	1161	11	5.29	0.05	22.37	1099	<2	0.19	1846	<10	<2	28	0.03	33	<10	83
46731	<1	3.33	917	2.2	<5	4.49	3	72	609	8	5.87	0.91	15.03	1280	2	0.35	1055	2022	15	589	0.35	89	<10	77
46732	<1	0.24	12	<0.5	<5	1.20	4	91	1248	10	5.28	0.02	21.69	981	<2	0.04	1935	44	<2	19	0.01	22	<10	69
46733	<1	0.37	63	<0.5	<5	2.72	3	93	1273	6	5.40	0.07	20.90	1204	2	0.05	1886	123	<2	80	0.03	23	<10	69
46734	<1	4.33	21	0.7	<5	2.42	3	69	737	14	6.14	0.12	17.06	3250	<2	0.11	1048	433	42	67	0.23	86	<10	197
46735	<1	1.58	17	<0.5	<5	1.83	4	88	1104	56	5.86	0.04	20.03	1572	<2	0.03	1671	175	93	49	0.08	50	<10	91
46741	<1	0.40	<10	<0.5	<5	0.44	3	79	1048	2	4.59	0.02	17.57	477	<2	0.03	1660	18	2	9	0.02	24	<10	64
46742	<1	0.32	<10	<0.5	<5	2.15	3	83	817	8	4.80	0.02	17.68	744	<2	0.04	1777	22	5	50	0.02	21	<10	59
46743	<1	5.09	18	0.9	<5	1.03	3	102	766	10	6.79	0.36	16.55	945	<2	0.27	1678	256	37	23	0.27	160	<10	81
46744	<1	2.07	11	<0.5	<5	2.31	3	91	1387	17	5.47	0.11	16.68	676	<2	0.27	1576	160	5	39	0.12	63	<10	63
46745	<1	3.43	13	0.5	<5	3.24	3	82	1173	94	6.33	0.05	15.65	1060	<2	0.14	1366	149	7	50	0.18	115	<10	63
46746	<1	0.63	11	<0.5	<5	2.08	4	98	1075	29	5.54	0.02	18.72	616	<2	0.04	1934	34	<2	62	0.04	37	<10	54
46747	<1	3.54	16	<0.5	<5	3.44	3	83	1004	100	5.76	0.03	15.99	919	<2	0.09	1453	213	9	73	0.16	108	<10	59
46748	<1	3.84	16	<0.5	<5	5.09	3	104	1322	169	6.52	0.05	15.52	1142	<2	0.13	1437	156	9	58	0.19	124	<10	76
46749	<1	2.25	15	<0.5	<5	3.85	4	89	1582	26	6.19	0.05	16.35	771	<2	0.16	1505	164	5	53	0.13	80	<10	59
46750	<1	0.71	<10	<0.5	<5	1.88	5	127	2008	239	7.07	0.02	18.83	757	<2	0.05	2144	15	<2	34	0.06	48	<10	67
46751	<1	1.14	11	<0.5	<5	2.69	4	105	1457	29	6.00	0.02	17.18	721	<2	0.07	1820	69	<2	44	0.07	56	<10	65
Duplicates:																								
46729	<1	0.61	54	<0.5	<5	1.41	4	109	1053	17	5.44	0.11	23.84	1107	2	0.14	2151	<10	7	23	0.03	32	<10	80
46743	<1	4.78	17	0.9	<5	1.00	3	99	869	9	6.74	0.30	16.34	940	<2	0.15	1608	266	27	22	0.28	155	<10	82
Standards:																								
Blank	<1	0.01	<10	<0.5	<5	<0.01	<1	1	3	<1	0.01	<0.01	0.01	<5	<2	0.01	2	<10	<2	<1	<0.01	<1	<10	<2
CH-4	2	7.88	465	1.6	<5	1.85	2	32	131	1985	5.38	1.73	1.42	454	2	3.14	56	657	18	209	0.32	99	<10	218

A .2 gm sample is digested with HNO3/HClO4/HF/HCL and diluted to 25 ml.



Assayers Canada
8282 Sherbrooke St.
Vancouver, B.C.
V5X 4R6
Tel: (604) 327-3436
Fax: (604) 327-3423

Quality Assaying for over 25 Years

Assay Certificate

8V-2582-PA1

Company: **WHY Resources**
Project:
Attn: Frank Marasco

Sep-17-08

We *hereby certify* the following assay of 23 pulp samples
submitted Jul-19-08

Sample Name	Au g/tonne	Ni-NiS ppm
43832	0.03	1039
43837	0.01	1076
43842	0.01	949
43847	<0.01	915
43852	<0.01	909
43857	0.02	982
43862	0.02	1265
43867	<0.01	1490
43872	<0.01	6
43882	0.03	3
43888	<0.01	1123
43893	<0.01	1149
43898	<0.01	1112
43903	<0.01	1335
43908	<0.01	1325
43913	<0.01	1087
43918	0.02	1138
43923	0.02	1262
43928	0.01	1135
43938	<0.01	1432
43948	<0.01	1342
43958	0.01	1641
43968	0.01	1136
*DUP 43832	n.e.s	1038
*DUP 43882	0.03	4
*DUP 43938	<0.01	1476
*0218	0.93	
*RTS-2		168
*BLANK	<0.01	<1

Certified by _____

August 28, 2008

Frank Marasco
West High Yield Resources
P.O Box 68121
Calgary, Alberta
Canada T3G 3N8
Ph. 403.283-5555
Fax. 403.206-7159

Dear Mr. Marasco,

Please find attached the third interim report of the results from the tests on the West High Yield Resources composite sample, received from Assayer's Canada, on June 6, 2008. This is not a final report.

Please feel free to contact us if you have any questions.

Sincerely,

Alex Lum,. P.Eng.
Metallurgical Engineer

Magnetic Separation and Gravity Test on WHY Samples, Interim Report

Prepared for:

West High Yield Resources
P.O Box 68121
Calgary, Alberta
Canada T3G 3N8
Ph. 403.283-5555
Fax. 403.206-7159
Attn: Frank Marasco

Prepared by:

Met-Solve Laboratories Inc.
8515 Eastlake Drive
Burnaby, BC
V5A 6R9
Canada

Project Number:

MS1103

Alex Lum, P.Eng
Metallurgical Engineer

Ish Grewal, M.A.Sc. P.Eng
President

August 28, 2008

Note: This report refers to the samples as received. The information contained in this report is provided 'as is' without warranty of any kind with respect to the interpretation and use of the data by the client.

1.0 BACKGROUND

Met-Solve received a bag of mineral sample, weighing approximately 12 kg, from Assayer's Canada bags, on June 6, 2008. According to Assayer's Canada, the sample is composed of:

3 Kg of 42844
4 Kg of 42845
4 Kg of 42846
1 Kg of 42847

Roughly half of the samples had been split out for use in previous tests; see Interim Reports 1 and 2. The remaining combined samples were ground and then subject to a centrifugal gravity concentration and magnetic separation. The tails from the magnetic separation was tested in two sulfuric acid leach tests. The centrifugal gravity test was done to check the gold recovery of a previous test.

The composite sample was ground to a P80 size of 103 μm using a lab scale rod mill, with 24 stainless steel rods, at a slurry pulp density of 40-50%. See back of appendix for particle size analysis.

2.0 GRAVITY CONCENTRATION.

A high mass yield gravity test (Falcon C-Machine simulation) was done to check the gold recovery found in prior gravity test, see XE101 in Interim Report 1. The detailed results are summarized in the Appendix, Gravity Concentration Test Report.

Precious metal assays done on the products found the silver, platinum and palladium grades to be very low. The gold grades were much lower than the values found in prior test. Gold recovery is summarized as follows.

Repeat Test, XE113

Products	Weight		Au	
	(g)	(%)	ppm	%Dist
SB40 Pan Concentrate 1	95.4	3.41	1.19	49.6
SB40 Pan Concentrate 2	123.4	4.41	0.20	10.8
SB40 PanConcentrate 3	92.2	3.29	0.29	11.7
SB40 Pan Concentrate 4	91.5	3.27	0.12	4.8
SB40 Pan Concentrate 5	76.8	2.74	0.07	2.4
SB40 Pan Tail 5	50.8	1.81	0.04	0.9
Total SB40 Concentrate	530.1	18.93	0.35	80.2
SB40 Tails	2,269.9	81.07	0.02	19.8
Calculated Head	2,800.0	100.00	0.08	100.0
Assayed Head			0.01	


Original Test, XE 101

Products	Weight		Au	
	(g)	(%)	ppm	%Dist
SB40 Pan Concentrate 1	5.26	0.14	436.40	26.5
SB40 Pan Concentrate 2	12.49	0.34	365.40	52.8
SB40 PanConcentrate 3	20.01	0.55	32.96	7.6
SB40 Pan Concentrate 4	16.65	0.45	29.58	5.7
SB40 Pan Concentrate 5	2.50	0.07	180.60	5.2
SB40 Pan Tail 5	85.00	2.32	0.12	0.1
Total SB40 Concentrate	141.91	3.87	59.71	98.0
SB40 Tails	3,529.05	96.13	0.05	2.0
Calculated Head	3,670.96	100.00	2.36	100.0
Assayed Head			0.05	

The repeat test had the samples assayed to extinction which eliminates errors due to the nugget effect. In the original test, the assayer did the gold assays twice due to the unexpectedly high values. The large discrepancy cannot be explained and further testing on new sample is required.

3.0 MAGNETIC SEPARATION

The results of the magnetic separation test are summarized in the Appendix, Gravity Concentration Test Report.

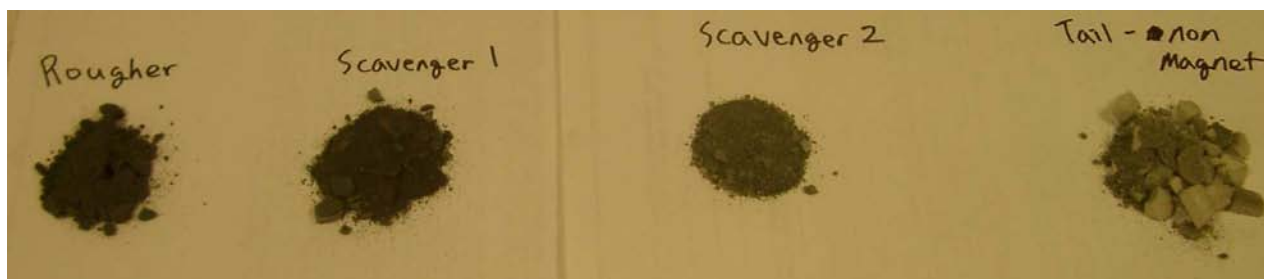

View of the different magnetic separation product. Note the darker colour of the rougher and scavenger 1.

The three stages, rougher and two scavengers, removed 27.5% of the mass, which recovered 55.2% of the magnetite (Fe_3O_4), 39.7% of the nickel and 67.3% of the chromium from the feed. The separation upgraded the magnesium, in the tails, from 22.5% to 23.2% while reducing the iron from 7.6% to 5.7%. Note that the back calculated heads concentration, from the leach tests indicated that the magnesium had been upgraded from 31.3% to 40.9% (see table in next section).

It is recommended to repeat this test on another set of samples to see if the separation can be improved.

4.0 SULFURIC ACID LEACH OF NON-MAGNETIC TAILS

Two sulfuric acid leach tests were done at a pulp density of 10-15 weight% solids on the non-magnetic tails. Sulfuric acid was used as it gave better results than hydrochloric acid in prior tests. The sulfuric acid is added as 95-98% w/w%, which corresponds to typical industrial grade.

The first test, XE116, was done under similar conditions to earlier test (test XE109). Acid was added as required to maintain **pH 1**. Subsamples were taken every half hour to monitor the kinetics. The concentrations of the subsamples are shown in the leach test report and these values show how quickly the metals are going into solution. The following table compares the results of the two 70°C leaches.

Test Feed	XE116 Non Mag Tails	XE109 Ore
Acid Consumption (kg/tonne)	980	974
%Wt Loss (feed to residue wt change)	43.3	46.0
Amount Mg into solution (%)	93.2	84.5
Mg in feed (ppm)	409,008	312,665
Mg in residue (ppm)	55,900	89,400
Amount Ni into solution (%)	69.4	44.2
Ni in feed (ppm)	2,695	2,830
Ni in residue (ppm)	1,663	2,923
Amount Fe into solution (%)	84.4	62.6
Fe in feed (ppm)	66,012	63,547
Fe in residue (ppm)	20,750	44,000
Amount Mn into solution (%)	94.9	84.3
Mn in feed (ppm)	1,737	1,338
Mn in residue (ppm)	178	388

Both tests used similar amounts of acid. The test on the non magnetic tails had better metal recovery and significantly lower metal concentration remaining in the leach residue. Note that the magnetic separation increased the grade of the magnesium which likely improved the leaching result.

It is recommended additional tests be conducted to improve upon current results.

5.0 EFFECT OF SULFURIC ACID LEVEL ON LEACH OF NON-MAGNETIC TAILS

The second leach test, XE117, done at 70°C, with incremental acid addition was conducted to estimate the magnesium recovery as a function of acid addition. There is a definite increase in magnesium recover with increasing acid. The following table shows the magnesium going into solution as a function of acid addition.

Acid kg/tonne	Mg Tenor (g/l)	%Mg Leached Into liquor
102	2.9	6.8%
300	7.9	18.9%
500	11.7	28.0%
705	26.2	62.7%
903	33.5	80.1%

These results are plotted in the appendix.

APPENDICES

Client: West High Yield Resources

Date: 14-Jul-08



Test: XE113

Project: MS1103

Sample: Composite from Assayer Canada ground to a P80 of 103µm

Products	Weight		Assay (ppm)		Distribution (%)	
	(g)	(%)	Au	Ag	Au	Ag
SB40 Pan Concentrate 1	95.4	3.41	1.19	0.00	49.6	0.0
SB40 Pan Concentrate 2	123.4	4.41	0.20	0.00	10.8	0.0
SB40 PanConcentrate 3	92.2	3.29	0.29	0.00	11.7	0.0
SB40 Pan Concentrate 4	91.5	3.27	0.12	0.00	4.8	0.0
SB40 Pan Concentrate 5	76.8	2.74	0.07	0.00	2.4	0.0
SB40 Pan Tail 5	50.8	1.81	0.04	0.00	0.9	0.0
Total SB40 Concentrate	530.1	18.93	0.35	0.00	80.2	0.0
SB40 Tails	2,269.9	81.07	0.02	0.50	19.8	100.0
Calculated Head	2,800.0	100.00	0.08	0.41	100.0	100.0
Assayed Head			0.01	0.10		

Products	Weight		Assay (ppm)		Distribution (%)	
	(g)	(%)	Pt	Pd	Pt	Pd
SB40 Pan Concentrate 1	95.4	3.41	0.01	0.00	43.6	
SB40 Pan Concentrate 2	123.4	4.41	0.01	0.00	56.4	
SB40 PanConcentrate 3	92.2	3.29	0.00	0.00	0.0	
SB40 Pan Concentrate 4	91.5	3.27	0.00	0.00	0.0	
SB40 Pan Concentrate 5	76.8	2.74	0.00	0.00	0.0	
SB40 Pan Tail 5	50.8	1.81	0.00	0.00	0.0	
Total SB40 Concentrate	530.1	18.93	0.00	0.00	100.0	
SB40 Tails	2,269.9	81.07	0.00	0.00	0.0	
Calculated Head	2,800.0	100.00	0.00	0.00	100.0	
Assayed Head			0.00	0.00		

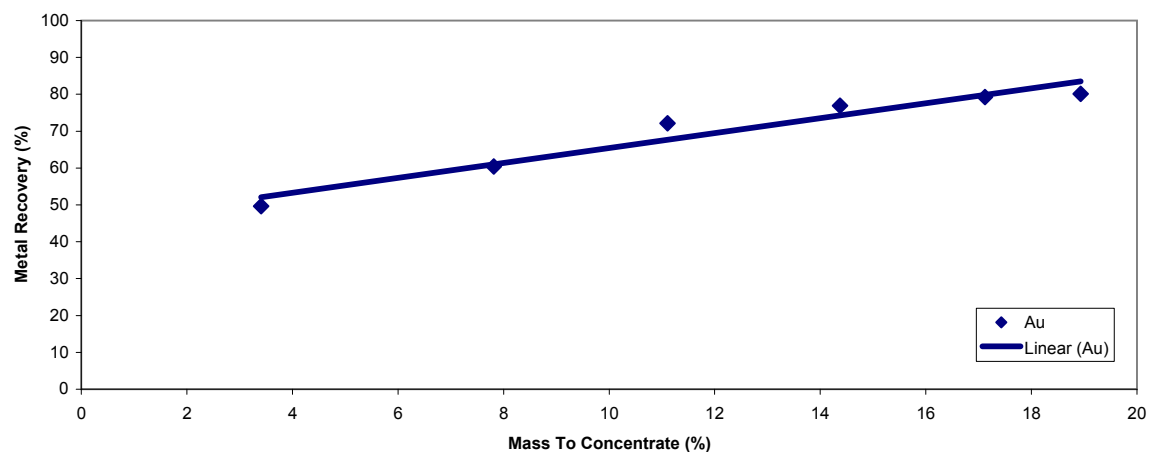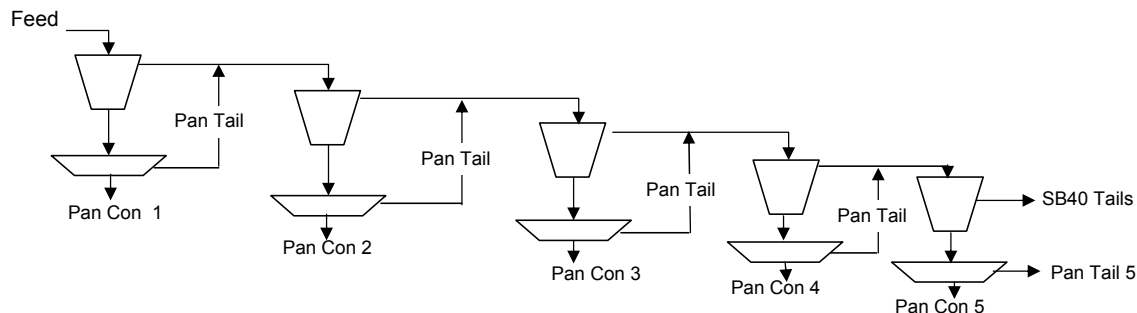



MAGNETIC SEPARATION TEST REPORT

Client: WHY

Test: XE114

Sample: Composite from Assayer Canada


Date: 13-Aug-08

Project: MS1103

Products	Weight		Assay (g/t)		Distribution (%)	
	(g)	(%)	Mg	Cr	Mg	Cr
Rougher Magnetic Con	284.2	10.7	191,000	13,600	9.1	38.8
Scavenger Magnetic Con 1	247.0	9.3	210,000	9,300	8.7	23.0
Scavenger Magnetic Con 2	195.2	7.4	227,000	2,800	7.4	5.5
Non-Magnetic Tail	1,919.4	72.5	232,000	1,700	74.7	32.7
Calculated Head	2,645.8	100.0	225,174	3,769	100.0	100.0
Assayed Head			241,000	6,490		

Products	Weight		Assay (g/t)		Distribution (%)	
	(g)	(%)	Fe ₃ O ₄	Fe	Fe ₃ O ₄	Fe
Rougher Magnetic Con	284.2	10.7	211,400	177,500	32.8	25.1
Scavenger Magnetic Con 1	247.0	9.3	135,600	123,000	18.3	15.1
Scavenger Magnetic Con 2	195.2	7.4	38,300	56,500	4.1	5.5
Non-Magnetic Tail	1,919.4	72.5	42,800	56,900	44.8	54.3
Calculated Head	2,645.8	100.0	69,240	75,995	100.0	100.0
Assayed Head			42,000	53,700		

Products	Weight		Assay (g/t)		Distribution (%)	
	(g)	(%)	Ni	Mn	Ni	Mn
Rougher Magnetic Con	284.2	10.7	4,121	1,129	19.6	12.2
Scavenger Magnetic Con 1	247.0	9.3	3,289	1,025	13.6	9.7
Scavenger Magnetic Con 2	195.2	7.4	1,972	972	6.5	7.2
Non-Magnetic Tail	1,919.4	72.5	1,872	968	60.3	70.9
Calculated Head	2,645.8	100.0	2,253	991	100.0	100.0
Assayed Head			2,467	1,080		

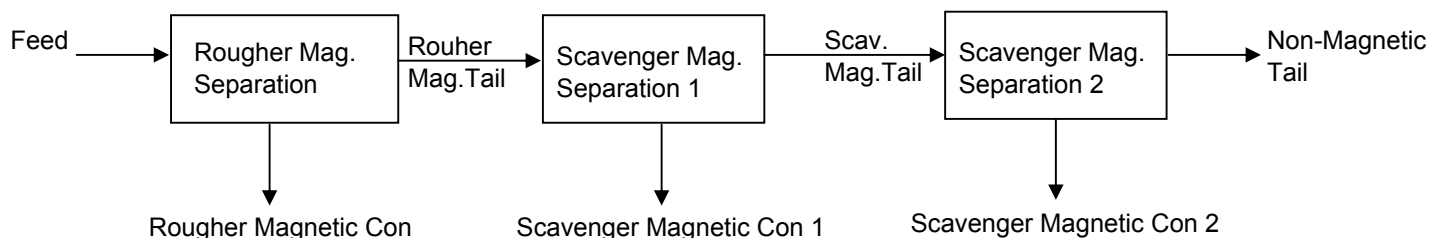

Test Conditions	
Pulp Density:	30 %
Flowrate:	1500 mL/min



LEACH TEST REPORT

Client: West High Yield Resources

Date: 29-Jul-08

Test: XE116

Project: MS1103

Sample: Magnetic separation Tails ground to 56 µm

70°C pH 1 Sulfuric Acid Leach

Total Acid Consumption 980 kg/tonne

Purpose: to repeat the 70°C pH 1 sulfuric acid leach on the tails from magnetic separation and determine if cleaning the ore by removing some magnetic components improves leaching results.

Products	Vol or Weight	Assay (ppm)		Distribution (%)	
		Mg	Ni	Mg	Ni
30 min sample	2.0 ml	17,700	101	0.1	0.1
60 min sample	2.5 ml	30,600	158	0.2	0.1
90 min sample	2.3 ml	35,900	183	0.2	0.2
Preg Sol	930.0 ml	41,300	201	90.2	66.8
Acid Rinse	505.0 ml	1,899	11	2.3	2.0
Water Rinse	275.0 ml	415	2	0.3	0.2
Residue	51.68 g	55,900	1,663	6.8	30.6
Calculated Head		409,008	2,695	100.0	100.0
Assayed Head	104.07 g	232,000	1,872		

Products	Vol or Weight	Assay (ppm)		Distribution (%)	
		Fe	Mn	Fe	Mn
30 min sample	2.0 ml	2,928	100	0.1	0.1
60 min sample	2.5 ml	4,648	146	0.2	0.2
90 min sample	2.3 ml	5,322	162	0.2	0.2
Preg Sol	930.0 ml	6,042	179	81.8	92.1
Acid Rinse	505.0 ml	267	8	2.0	2.1
Water Rinse	275.0 ml	52	1	0.2	0.2
Residue	51.68 g	20,750	178	15.6	5.1
Calculated Head		66,012	1,737	100.0	100.0
Assayed Head	104.07 g	56,900	968		



LEACH TEST REPORT

Client: West High Yield Resources

Date: 30-Jul-08

Test: XE117

Project: MS1103

Sample: Magnetic separation Tails ground to 56 µm

70°C Sulfuric Acid Leach

Total Acid Consumption


903 kg/tonne

Purpose: to leach the magnetic separation tails at 70°C with increasing acid level to estimate magnesium recovery as a function of acid consumption.

Products	Vol or Weight	Assay (ppm)		Distribution (%)	
		Mg	Ni	Mg	Ni
30 min: 100 kg/t acid, pH 4	3.9 ml	2,863	33	0.0	0.0
60 min: 300 kg/t acid, pH1.8	4.5 ml	7,920	65	0.1	0.1
90 min: 500 kg/t acid, pH 1.3	2.5 ml	11,700	82	0.1	0.1
120 min: 700 kg/t acid pH 1.2	4.0 ml	26,200	153	0.3	0.2
Preg Sol: 900 kg/t acid pH 1.1	880.0 ml	33,500	180	78.8	59.7
Acid Rinse	505.0 ml	1,620	10	2.2	1.9
Water Rinse	224.0 ml	203	1	0.1	0.1
Residue	56.73 g	121,300	1,765	18.4	37.8
Calculated Head		373,796	2,646	100.0	100.0
Assayed Head	100.07 g	232,000	1,872		

Products	Vol or Weight	Assay (ppm)		Distribution (%)	
		Fe	Mn	Fe	Mn
30 min: 100 kg/t acid, pH 4	3.9 ml	63	35	0.0	0.1
60 min: 300 kg/t acid, pH1.8	4.5 ml	884	62	0.1	0.2
90 min: 500 kg/t acid, pH 1.3	2.5 ml	1,794	76	0.1	0.1
120 min: 700 kg/t acid pH 1.2	4.0 ml	4,114	144	0.3	0.0
Preg Sol: 900 kg/t acid pH 1.1	880.0 ml	5,102	163	73.9	86.3
Acid Rinse	505.0 ml	196	7	1.6	2.1
Water Rinse	224.0 ml	22	1	0.1	0.1
Residue	56.73 g	25,700	325	24.0	11.1
Calculated Head		60,725	1,656	100.0	100.0
Assayed Head	100.07 g	56,900	968		

Magnesium Recover vs Acid Consumption of Magnetic Separation Tails

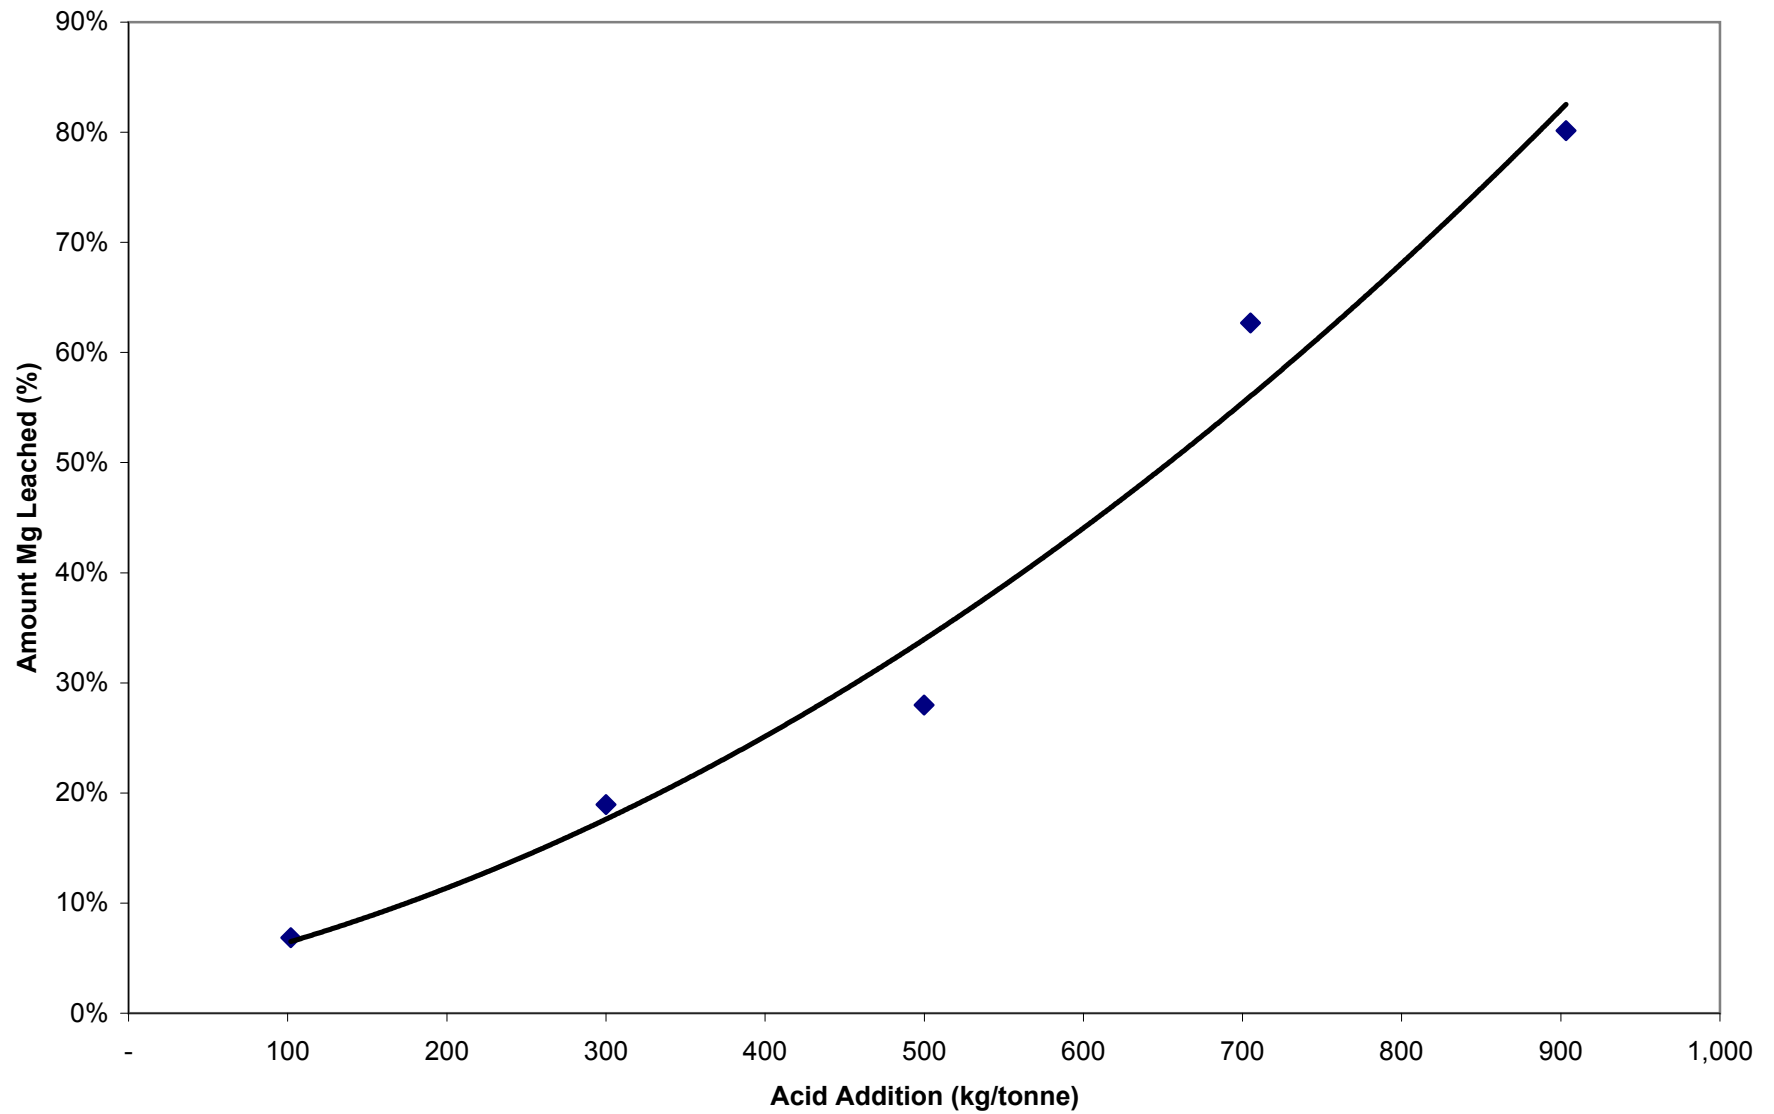

PARTICLE SIZE ANALYSIS

Client: WHY Resources

Test: XE115

Sample: 10 min Grind; feed for XE113

Date: 17-Jul-08

Project: MS1103



Sieve Size		Weight		Cumulative (%)	
Tyler Mesh	Microns	(g)	(%)	Retained	Passing
8	2360	0.0			
10	2000	0.0			
16	1180	0.0			
20	850	0.0			
30	600	0.0			
40	425	0.0			
50	300	0.0			
70	212	0.0			
100	150	8.7	9.78	9.78	90.22
140	106	9.6	10.79	20.56	79.44
200	75	10.2	11.46	32.02	67.98
270	53	11.6	13.03	45.06	54.94
400	37	9.7	10.90	55.96	44.04
Undersize	-53	39.2	44.04	100.00	
TOTAL:		89.0	100.0		

Rosin-Rammler Model

Size (um)	Passing P (%)
103	80
46	50

Linear Interpolation

Size (um)	Passing P (%)
108	80
46	50

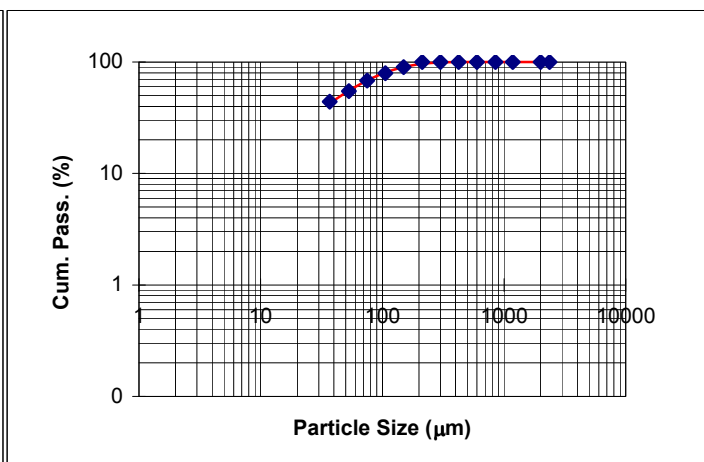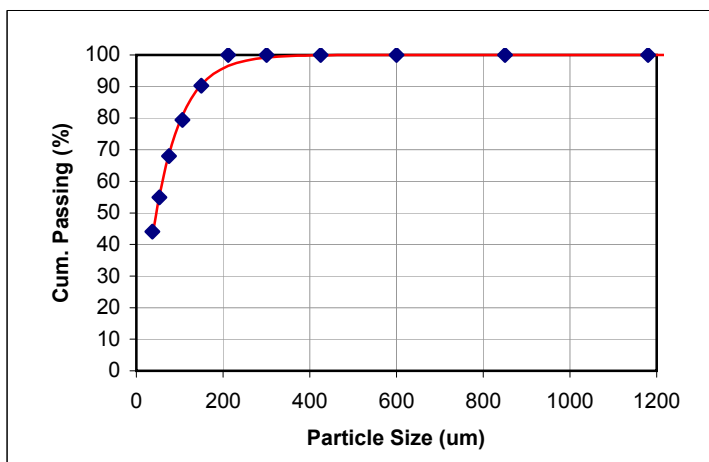

October 28, 2008

Frank Marasco
West High Yield Resources
P.O Box 68121
Calgary, Alberta
Canada T3G 3N8
Ph. 403.283-5555
Fax. 403.206-7159

Dear Mr. Marasco,

Please find attached the final report of the results from the tests on the West High Yield Resources sample, received on August 27, 2008.

Please feel free to contact us if you have any questions.

Sincerely,

Alex Lum,. P.Eng.
Metallurgical Engineer

**Magnesium Recovery from WHY
Resources Samples;
Supplementary Tests
Report #2**

Prepared for:

West High Yield Resources
P.O Box 68121
Calgary, Alberta
Canada T3G 3N8
Ph. 403.283-5555
Fax. 403.206-7159
Attn: Frank Marasco

Prepared by:

Met-Solve Laboratories Inc.
8515 Eastlake Drive
Burnaby, BC
V5A 6R9
Canada

Project Number:

MS1103

Alex Lum, P.Eng
Metallurgical Engineer

Ish Grewal, M.A.Sc. P.Eng
President

October 28, 2008

Note: This report refers to the samples as received. The information contained in this report is provided 'as is' without warranty of any kind with respect to the interpretation and use of the data by the client.

1.0 BACKGROUND

Met-Solve received a crate of mineral samples, weighing approximately 200 kg on August 27, 2008. The crate, containing eight large bags, was shipped from:

WHY Resources
Casa El Pina Room #10
Rossland, BC
Ph: 250-231-4451


Inside the large bags were 111 small bags, with sample numbers ranging from 42844 to 44865, each containing “1/4 split” drill core samples.

This report provides an update on supplementary leaching tests to those summarized in the previous report (Report 1). The objective of the tests was to examine the leaching kinetics and acid consumption by leaching hydrochloric acid at elevated temperatures (70°C).

2.0 METHODOLOGY

The 200 kg of sample was crushed and mixed. A representative 10 kg sample was cut out and ground in the rod mill for 10 minutes. Representative samples were taken from the ground material and used for screen analysis (test XE119), acid consumption leach test (test XE120) and kinetics leach test (test XE121).

The leaches were run with a 5% pulp density at 70°C. Bottle strength (~37%) hydrochloric acid was used (note that 37% HCl corresponds to typical industrial grade). The leach tests were conducted according the following general flow sheet.

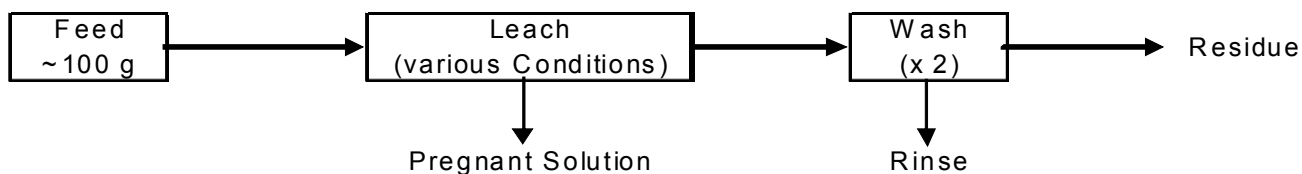

3.0 RESULTS

For the acid consumption test, acid was added and allowed to stabilize for 30 minutes at which time the liquor was sampled. This was repeated four times to get a profile of magnesium leached as a function of acid addition. The results are summarized in Table 1.

Table 1: Magnesium Recovery as a Function of Hydrochloric Acid

HCl Addition (kg/tonne)	[Mg] in Sol'n (g/l)	Mg Leached (%)
202	2.2	8.7%
600	4.1	16.0%
998	7.0	27.4%
1,396	9.2	35.7%
1,796	16.7	65.2%

As expected, the amount of magnesium leached increases with increasing acid addition.

For the leaching kinetics test, the full amount of acid, 1,814 kg/tonne, was added up front and samples were taken at various times to get a profile of magnesium recovery as a function of time. The results are summarized in Table 2.

Table 2: Magnesium Recovery Kinetics

Time (minutes)	[Mg] in Sol'n (g/l)	Mg Leached (%)
-	0.1	0.3%
15	5.2	22.2%
30	8.7	36.9%
60	11.0	46.7%
150	15.4	65.4%
240	18.5	78.6%

The full results and leaching kinetics plots are summarized in the appendix along with the complete final pregnant solution ICP assays and the particle size analyses. In the leach test reports, there is a significant difference in the calculated and assayed head values. The calculated heads are believed to be more accurate as it is more in line with previous values. The head assay should be redone in future tests.

7.0 RECOMMENDATIONS

Since no tests were done examining the effect of grind size, future test work should examine the effect of particle size on leach kinetics and acid consumption. This can be done by either grinding to different particles sizes or using screened material for the tests.

Solutions from leaching will most likely require purification prior to further downstream processing. Hence, test work should also be conducted on solution purification via pH adjustment followed by solvent extraction and/or ion exchange.

.

APPENDICES



LEACH TEST REPORT

Client: West High Yield Resources

Date: 29-Sep-08

Test: XE120

Project: MS1103

Sample: New Head Ore, ground to a P80 of 841 μm

70°C Hydrochloric Acid Leach

Soilds wt loss: 30.8%

Total Acid Consumption

998 kg/tonne


HCl added as bottle strength, 37%

Purpose: to leach the composite head ore at 70°C with increasing acid level to estimate magnesium recovery as a function of acid consumption. The HCl acid was added as standard grade, 37%.

Products	Vol or Weight	Assay (ppm)		Distribution (%)	
		Mg	Ni	Mg	Ni
30 min: 200 kg/t acid, pH	3.1 ml	2,237	35	0.0	0.0
60 min: 600 kg/t acid, pH	4.1 ml	4,086	46	0.1	0.1
90 min: 1,000 kg/t acid, pH	4.6 ml	7,020	66	0.1	0.1
120 min: 1,400 kg/t acid pH	4.2 ml	9,150	77	0.1	0.1
Preg Sol: 1,800 kg/t acid pH	1,060.0 ml	16,700	123	64.3	47.4
Acid Rinse	345.0 ml	1,609	14	2.0	1.7
Water Rinse	345.0 ml	617	6	0.8	0.7
Residue	69.70 g	128,900	1,977	32.6	49.9
Calculated Head		273,547	2,743	100.0	100.0
Assayed Head	100.71 g	204,000	2,080		

Products	Vol or Weight	Assay (ppm)		Distribution (%)	
		Fe	Mn	Fe	Mn
30 min: 200 kg/t acid, pH	3.1 ml	262	28	0.0	0.1
60 min: 600 kg/t acid, pH	4.1 ml	629	38	0.0	0.1
90 min: 1,000 kg/t acid, pH	4.6 ml	1,077	49	0.1	0.2
120 min: 1,400 kg/t acid pH	4.2 ml	1,351	54	0.1	0.2
Preg Sol: 1,800 kg/t acid pH	1,060.0 ml	2,399	81	39.1	72.6
Acid Rinse	345.0 ml	260	9	1.4	2.7
Water Rinse	345.0 ml	103	4	0.5	1.1
Residue	69.70 g	54,800	389	58.7	23.0
Calculated Head		64,562	1,169	100.0	100.0
Assayed Head	100.71 g	60,800	848		

XE120: Magnesium Recovery vs Acid Consumption of Head Ore at 70°C

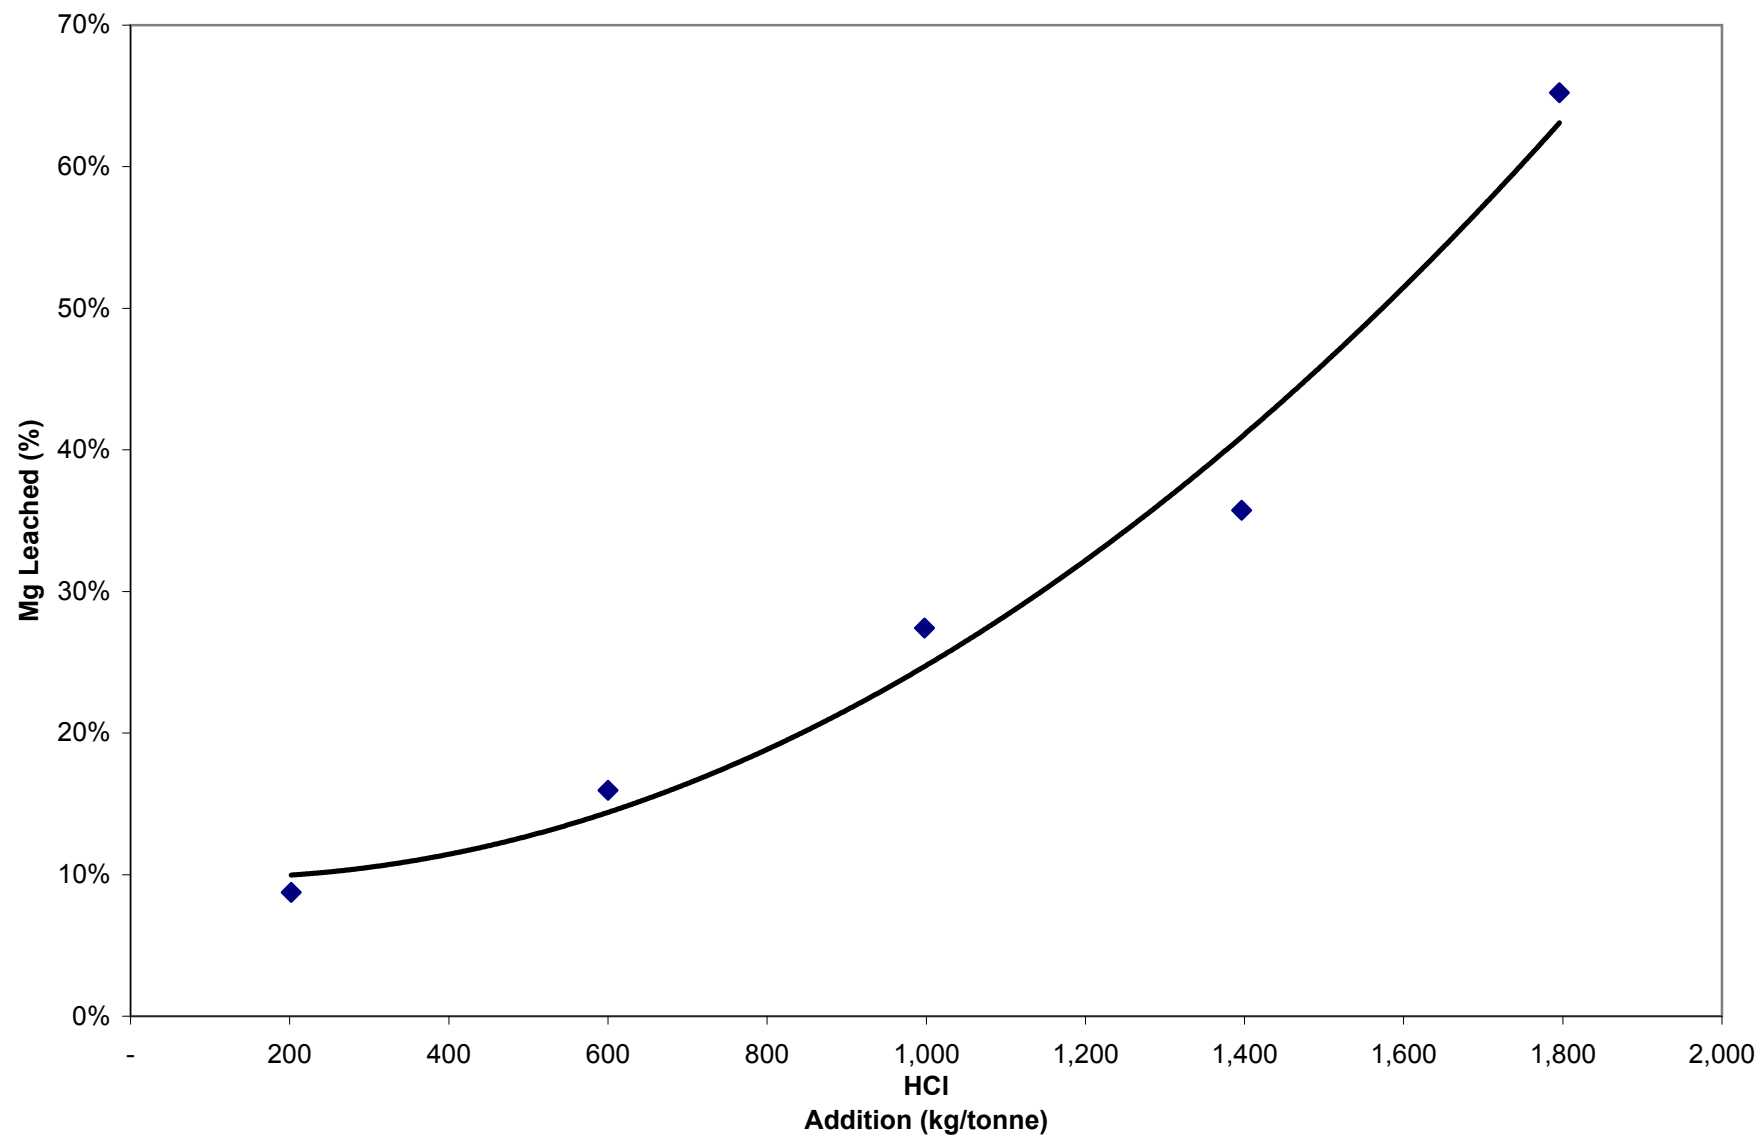



LEACH TEST REPORT

Client: West High Yield Resources

Date: 30-Sep-08

Test: XE121

Project: MS1103

Sample: New Head Ore, ground to a P80 of 841 µm

70°C Hydrochloric Acid Leach

Solids wt loss: **38.0%**

Total Acid Consumption

1,814 kg/tonne (of bottle strength, 37%)

Purpose: to leach the composite head ore at 70°C; intermittent samples were taken to estimate magnesium leaching kinetics.


Products	Vol or Weight	Assay (ppm)		Distribution (%)	
		Mg	Ni	Mg	Ni
0 min	3.8 ml	76	2	0.0	0.0
15 min	4.1 ml	5,230	41	0.1	0.1
30 min	4.1 ml	8,690	62	0.1	0.1
60 min	3.6 ml	11,000	80	0.2	0.1
150 min	4.2 ml	15,400	106	0.2	0.2
Preg Sol: 240 minutes	1,080.0 ml	18,500	127	77.2	55.7
Acid Rinse	365.0 ml	1,683	13	2.4	2.0
Water Rinse	110.0 ml	292	3	0.1	0.1
Residue	62.21 g	82,000	1,649	19.7	41.7
Calculated Head		258,038	2,450	100.0	100.0
Assayed Head	100.33 g	204,000	2,080		

Products	Vol or Weight	Assay (ppm)		Distribution (%)	
		Fe	Mn	Fe	Mn
0 min	3.8 ml	1	1	0.0	0.0
15 min	4.1 ml	821	33	0.1	0.1
30 min	4.1 ml	1,293	49	0.1	0.2
60 min	3.6 ml	1,587	57	0.1	0.2
150 min	4.2 ml	2,148	68	0.2	0.3
Preg Sol: 240 minutes	1,080.0 ml	2,558	75	48.6	78.9
Acid Rinse	365.0 ml	273	8	1.8	2.8
Water Rinse	110.0 ml	45	2	0.1	0.2
Residue	62.21 g	44,900	287	49.1	17.3
Calculated Head		56,647	1,029	100.0	100.0
Assayed Head	100.33 g	60,800	848		

Magnesium Recovery as a Function of Time

Time (minutes)	Mg Conc (g/l)	Mg Leached (%)
-	0.1	0.3%
15	5.2	22.2%
30	8.7	36.9%
60	11.0	46.7%
150	15.4	65.4%
240	18.5	78.6%

XE121: Kinetics of Magnesium Recovery, New Head Ore

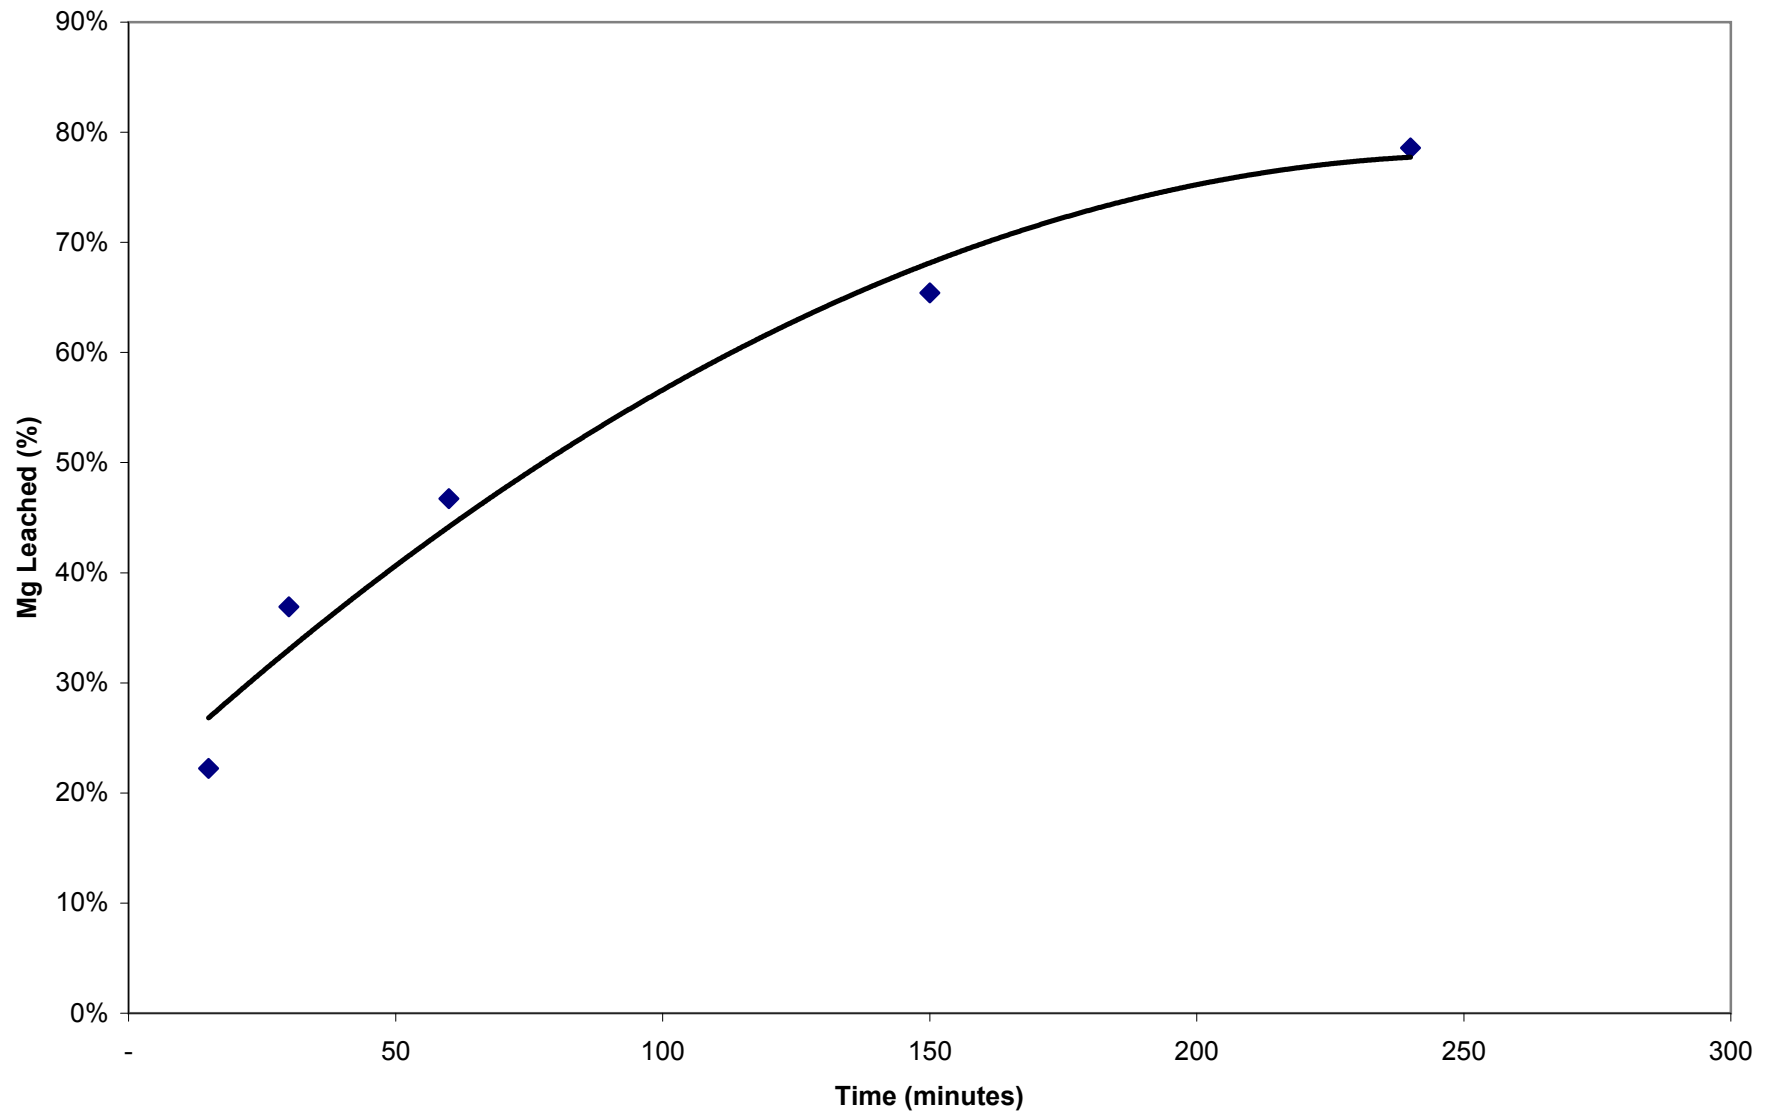



WHY Resources Preg Solution ICP Summary

Sample Name	Sample Description	ICP Ag µg/ml	ICP Al µg/ml	ICP As µg/ml	ICP B µg/ml	ICP Ba µg/ml	ICP Be µg/ml	ICP Bi µg/ml	ICP Ca µg/ml	ICP Cd µg/ml	ICP Co µg/ml	ICP Cr µg/ml	ICP Cu µg/ml	ICP Fe µg/ml	ICP Hg µg/ml	ICP K µg/ml	ICP La µg/ml	ICP Mg µg/ml	ICP Mn µg/ml
75926	XE120 Preg	<0.05	<1	2.7	16	4	<0.05	<0.5	527	0.3	4.4	14.3	1.5	2,399	0.2	4	0.1	16,700	80.6
75941	XE121 Preg	<0.05	7	2.8	<1	1	<0.05	<0.5	449	0.1	4.6	18.3	1	2,558	<0.1	<1	<0.1	18,500	75.4

Sample Name	Sample Description	ICP Mo µg/ml	ICP Na µg/ml	ICP Ni µg/ml	ICP P µg/ml	ICP Pb µg/ml	ICP S µg/ml	ICP Sb µg/ml	ICP Sc µg/ml	ICP Sr µg/ml	ICP Th µg/ml	ICP Ti µg/ml	ICP Tl µg/ml	ICP U µg/ml	ICP V µg/ml	ICP W µg/ml	ICP Zn µg/ml	ICP Zr µg/ml
75926	XE120 Preg	<2	<0.01	3	107	8	<0.01	<5	2	<1	139	0.08	43	134	11	<10	<1	5
75941	XE121 Preg	<2	<0.01	1	22	<2	0.01	<5	<1	<1	13	0.02	<10	<10	3	<10	<1	1

PARTICLE SIZE ANALYSIS

Client: WHY Resources

Test: XE119 (XE118 sample ground 10 minutes in rod mill)

Sample: Ground (10 min) mixed sample, from 200 kg shipment, Aug 27, 2008

Date: 23-Sep-08

Project: MS1103



Sieve Size		Weight		Cumulative (%)	
Tyler Mesh	Microns	(g)	(%)	Retained	Passing
8	2,360	0.0			
10	2,000	0.0			
16	1,180	0.0			
20	850	0.0			
30	600	164.8	49.34	49.34	50.66
40	425	26.8	8.02	57.37	42.63
50	300	23.7	7.10	64.46	35.54
70	212	17.8	5.33	69.79	30.21
100	150	15.5	4.64	74.43	25.57
140	106	13.0	3.89	78.32	21.68
200	75	9.7	2.90	81.23	18.77
270	53	10.7	3.20	84.43	15.57
400	37	7.5	2.25	86.68	13.32
Undersize	-53	44.5	13.32	100.00	
TOTAL:		334.0	100.0		

Rosin-Rammler Model

Size (um)	Passing P (%)
841	80
384	50

Linear Interpolation

Size (um)	Passing P (%)
749	80
586	50

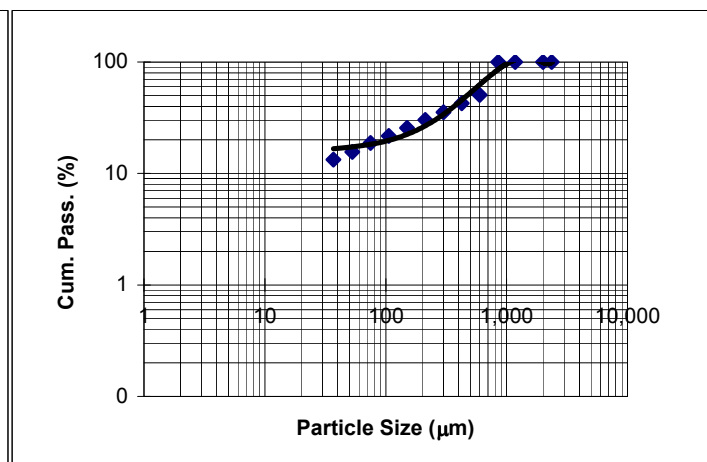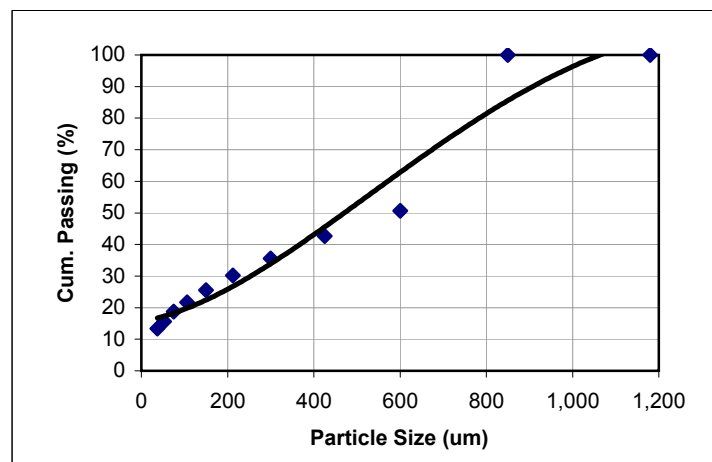

PETROGRAPHIC REPORT ON 4 SAMPLES FROM IVANHOE PROJECT, ROSSLAND
B.C.

Aug. 25, 2008.

SUMMARY:

One sample (RRS08-22 7.5) is pyroxene (?) monzodiorite/monzogabbro porphyry; one (RRS08-23 12.8) is (likely related) biotite-pyroxene-plagioclase phyric monzodiorite porphyry (both with accessory magnetite-ilmenite-sphene $\pm$ apatite-pyrite), and one sample (RRS08-23 47.3) is serpentine-talc/sericite-magnetite-carbonate-Mg chlorite-altered ultramafic rock (possibly wehrlite?) with accessory chromite and minor sulfides (mainly pyrrhotite, trace pentlandite?), also replaced by magnetite. Capsule descriptions are as follows:

RRS08-22 7.5: pyroxene (?) monzodiorite/monzogabbro porphyry (accessory quartz, magnetite-ilmenite-sphene), largely altered to actinolite-biotite-carbonate-quartz-sericite-chlorite-allanite (?).

RRS08-23 12.8: biotite-pyroxene-plagioclase phyric monzodiorite porphyry, with accessory magnetite-ilmenite-pyrite-sphene-apatite, slightly (deuteric) altered to secondary biotite-calcite-chlorite-clay?/sericite.

RRS08-23 47.3: peridotite, possibly wehrlite?) originally composed of about 20-25% intercumulus pyroxene (now pseudomorphed by talc/sericite-carbonate-magnetite-minor Mg-chlorite and green biotite) and 70% cumulus olivine (pseudomorphed by serpentine, minor magnetite and carbonate) plus accessory chromite and trace sulfides (also part replaced by secondary magnetite and carbonate).

Detailed petrographic descriptions and photomicrographs are appended (on CD). If you have any questions regarding the petrography, please do not hesitate to contact me.

Craig H.B. Leitch, Ph.D., P. Eng. (250) 653-9158 craig.leitch@gmail.com
492 Isabella Point Road, Salt Spring Island, B.C. Canada V8K 1V4

RRS08-22 7.5: PYROXENE (?) PHYRIC MONZODIORITE/MONZOGABBRO
PORPHYRY, ALTERED TO ACTINOLITE-BIOTITE-CARBONATE- SERICITE-
RUTILE

Hand sample shows medium to dark grey, fine-grained, porphyritic rock composed of 10-15% 2-3 mm phenocrysts of uncertain identity in an aphanitic groundmass. The rock is magnetic, shows no reaction to cold dilute HCl, and modest yellow stain for K-feldspar in the groundmass of the etched offcut (which reveals the phenocrysts to be mafic). It is similar in many aspects to sample RRS08-18 90.2 in the previous report. Modal mineralogy in polished thin section is approximately:

Amphibole (phenocrysts and groundmass; tremolite-actinolite?)	35%	
Biotite (brown, partly chloritized; green secondary)		25%
Plagioclase (andesine?)	20%	
K-feldspar (primary, groundmass; minor secondary)		10%
Carbonate (mainly ankerite?)		5%
Magnetite, ilmenite		2%
Quartz (primary and secondary)	1%	
Sphene		~1%
Sericite	<1%	
Chlorite	<1%	
Allanite (?)		<1%

This sample consists mainly of about 15-20% relict (actinolite-biotite-carbonate-minor Kspar-quartz-allanite? altered) mafic phenocrysts, possibly mainly after pyroxene (?), set in a finely crystalline groundmass of plagioclase, lesser K-feldspar, and mafics, altered to secondary biotite-actinolite-minor chlorite-sericite, with accessory quartz, magnetite-ilmenite-sphene.

Altered mafic phenocrysts have mainly euhedral outlines up to about 2 mm that are pseudo-morphed by amphibole (larger, carbonate altered relict pyroxenes are up to 3 mm). The amphibole is generally pale green, with small extinction angle about 15 degrees and fibrous habit (lath-shaped crystals rarely over about 1 mm long), suggestive of actinolite (?), and it is intimately intergrown with brownish green secondary biotite as subhedral, randomly oriented flakes mostly <0.2 mm in diameter. However, in the carbonate-altered type, the amphibole is almost colourless, suggestive of tremolite (?). Carbonate in these forms interlocking subhedra <0.35 mm in size that are probably mostly ankerite to judge by the lack of reaction in hand specimen. Accessory sphene (rounded subhedra mostly <20 microns) is common. In places, minor K-feldspar and quartz (subhedra <0.25 mm in size) are also present, associated with brown allanite (?) <0.1 mm.

In the groundmass, plagioclase forms interlocking, randomly oriented, mainly euhedral lath-shaped crystals <0.5 mm long that are generally moderately to locally strongly altered to brownish green secondary biotite mostly <35 microns in size, plus minor minute (<20 micron) flakes of sericite. The plagioclase crystals typically retain traces of compositional zoning, particularly around the rims, but composition is difficult to ascertain due to the alteration (could be around An50, based on extinction on 010 up to 30 degrees, with narrow more sodic rims). Most K-feldspar forms much finer-grained material, interstitial to or surrounding the plagioclase. Minor primary quartz forming subhedra <0.1 mm is interstitial. Lath-like amphibole (also actinolitic) and lesser flakes of biotite mostly <0.35 and <0.2 mm in diameter (both largely altered to brownish green secondary biotite) are associated with very fine-grained sphene and opaque oxides (mainly magnetite, ilmenite) all mostly <25 microns in size, generally evenly disseminated throughout the groundmass.

In summary, this may be pyroxene (?) monzodiorite/monzogabbro porphyry (accessory quartz, magnetite-ilmenite-sphene), largely altered to actinolite-biotite-carbonate-quartz-sericite-chlorite-allanite (?).

RRS08-23 12.8: BIOTITE-CLINOPYROXENE-PLAGIOCLASE PHYRIC MONZODIORITE PORPHYRY (ACCESSORY MAGNETITE-ILMENITE-PYRITE-APATITE) ALTERED TO BIOTITE-CHLORITE-CALCITE-CLAY?/SERICITE

Hand specimen shows massive, relatively fresh (unaltered) medium grey, plagioclase-biotite phyric porphyry of intermediate composition. The rock is magnetic, shows minor reaction to cold dilute HCl, and weak yellow stain for K-feldspar in the etched offcut, which reveals a xenolith or megacryst of more felsic material (rimmed by plagioclase), about 1.5 cm across. Modal mineralogy in polished thin section is approximately:

Plagioclase (oligoclase-andesine?)	45%
K-feldspar (mainly primary, groundmass, xenocryst)	20%
Biotite (primary)	10%
(secondary)	5%
Relict clinopyroxene	5%
Carbonate (mainly calcite?)	5%
Chlorite	5%
Magnetite, minor ilmenite	2%
Clay?/sericite (after feldspars)	1-2%
Sphene	<1%
Pyrite	<1%
Apatite	<1%

This sample consists of ~25% 1-3 mm plagioclase, 10-15% relict (calcite-chlorite altered) clinopyroxene, 10% 1-2 mm biotite, and minor opaque oxide/sulfide phenocrysts set in an aphanitic, felsic groundmass. The xenolith (xenocryst?) or megacryst is composed mainly of plagioclase (partly altered to Kspar, calcite, and clay?/sericite, and containing minor relict pyroxene).

Plagioclase phenocrysts have mainly euhedral, locally glomeratic outlines up to almost 5 mm in diameter (larger crystals occur in the xenocryst/megacryst). They show slight compositional zoning (particularly near rims) but vary little from about An₃₀ (oligoclase-andesine). They show local alteration to minute particles of clay?/sericite, especially within the xenocryst, where they are partly replaced by (?), or associated with, minor K-feldspar as sub/euhedral crystals up to 3 mms.

Relict clinopyroxene phenocrysts have mainly euhedral, but corroded, outlines up to about 2.5 mm long. The remaining pyroxene shows pale green colour (but no pleochroism) and large extinction angle around 40 degrees, suggestive of augite (?). They are partly to largely replaced by intimately intergrown carbonate (likely mostly calcite, forming ragged interlocking subhedra <0.25 mm in diameter) and chlorite (aggregates to 0.2 mm of subhedral flakes <0.1 mm with pale green pleochroism and near-zero birefringence, suggestive of F:M around 0.5?), and are associated with euhedral prismatic apatite to 0.35 mm and opaque oxides (mainly magnetite, minor ilmenite) as interlocking sub/euhedra mostly <2 mm in size.

Biotite phenocrysts have euhedral outlines up to 2 mm in diameter, commonly with narrow dark rims, and containing euhedral inclusions of apatite and Kspar <0.2 mm long. Pleochroism is from pale yellow to bright reddish-brown. Small phenocrysts (glomeratic to 1.5 mm) of opaque oxides are mainly composed of subhedral ilmenite (to 0.6 mm) and lesser magnetite (<0.35 mm). In places, these also contain minor pyrite (mainly cubic, <0.4 mm, containing trace galena <0.1 mm).

The groundmass consists mainly of alkali feldspar (plagioclase and Kspar, in ratio that is hard to define) forming mainly euhedral, interlocking, randomly oriented laths <0.35 mm long. They are generally partly altered to fine flakes of secondary biotite (euhedral, <45 microns in diameter), minute particles of clay?/sericite, and carbonate (mainly calcite, ragged subhedra <35 microns). Interstitial mafics are altered to chlorite, calcite, and biotite, and associated with opaque oxides (mainly ilmenite, <50 microns long) and sphene (sub/euhedra <45 microns in size).

In summary, this would be classed as biotite-pyroxene-plagioclase phyrlic monzodiorite porphyry, with accessory magnetite-ilmenite-pyrite-sphene-apatite, slightly (deuteric) altered to secondary biotite-calcite-chlorite-clay?/sericite.

RRS08-23 47.3: SERPENTINE-TALC/SERICITE-SECONDARY MAGNETITE-CARBONATE-MINOR MG CHLORITE ALTERED ULTRAMAFIC (PERIDOTITE, POSSIBLY WEHRLITE?) WITH ACCESORY CHROMITE, TRACE SULFIDES PARTLY REPLACED BY MAGNETITE

Hand specimen shows dark blackish green, fine-grained, altered looking ultramafic rock, but with a mottled texture caused by paler-coloured, probable intercumulus relict pyroxene (?). The rock is strongly magnetic, but shows only trace reaction to cold dilute HCl, and no stain for K-feldspar in the etched offcut. Modal mineralogy in polished thin section is approximately:

Serpentine (after olivine?)	65%
Talc/sericite (after pyroxene?)	25%
Magnetite (mainly secondary)	2-3%
Carbonate (partly calcite)	2-3%
Mg-chlorite	2-3%
Chromite (primary, relict)	1-2%
Sulfides (pyrrhotite, trace pentlandite?)	<1%
Secondary green (ferriferous) biotite	<1%

This sample appears to be composed of about 20-25% relict (talc/sericite-minor carbonate-magnetite-Mg chlorite-green biotite altered) intercumulus pyroxene sites in a matrix of relict (serpentine-magnetite altered) cumulus olivine, with accessory interstitial chromite and trace sulfides (both also partly replaced by secondary magnetite).

The main mass of the slide consists of fine-grained, more or less randomly oriented serpentine as subhedral flakes up to about 0.2 mm in diameter, principally pseudomorphing what probably were originally cumulus olivine crystals possibly up to about several mm across (?). The former boundaries of the olivine crystals are marked by discontinuous microveinlets of secondary magnetite (locally with minor carbonate) mostly <0.15 mm thick; similar veinlets also cut across the olivine sites.

Possible former intercumulus pyroxene sites with ragged, irregular to rarely subhedral outlines up to about 4 mm across are marked by relatively coarse-grained talc/sericite as mainly euhedral, bladed or lath-shaped crystals up to about 0.6 mm in diameter. It is possible that minor colourless amphibole (tremolite) is mixed with the talc/sericite, but this is difficult to confirm. In places, minor carbonate (ragged subhedra mostly <0.25 mm in diameter), fine-grained secondary magnetite, and local Mg-chlorite (euhedral flakes up to 50 microns with distinctive length-fast, first-order grey/white birefringence suggestive of F:M around 0.4?) or rare bright green (Fe-rich) secondary biotite as euhedral flakes <35 microns, are also present in these sites.

Chromite occurs as relatively coarse, somewhat skeletal sub/euhedral crystals up to about 2 mm in diameter, generally partly replaced along fractures and at rims by secondary

magnetite (and carbonate). Most of the sulfide is so very fine-grained (typically <50 microns) and heavily replaced by secondary magnetite that it is difficult to identify. It appears to be mainly pyrrhotite, locally with very minor inclusions or “flames” of pentlandite mostly <15 microns thick. Secondary magnetite replacing both chromite and sulfides, as well as along discontinuous microveinlets in the adjacent altered wallrock, generally forms minute sub/euhedral crystals <15, but locally aggregating to 50, microns in diameter.

In summary, this appears to represent ultramafic rock (likely peridotite, possibly wehrlite) originally composed of about 20-25% intercumulus pyroxene (now pseudomorphed by talc/sericite-carbonate-magnetite-minor Mg-chlorite and green biotite) and 70% cumulus olivine (pseudomorphed by serpentine, minor magnetite and carbonate) plus accessory chromite and trace sulfides (also partly replaced by secondary magnetite and carbonate).

PHOTOMICROGRAPH CAPTIONS

RRS08-22 7.5: Relict mafic (pyroxene?) phenocrysts altered to actinolitic amphibole (ac) or carbonate (cb), tremolite (tr) and minor quartz (qz) and Kspar (Kf), in groundmass of plagioclase laths and amphibole (both altered to brownish green secondary biotite), magnetite/ilmenite (opaque) and sphene. Transmitted plane light, field of view 3.0 mm wide.

RRS08-23 12.8: Phenocrysts of plagioclase (PL, slightly altered to clay?/sericite around rims), biotite (BI), and relict clinopyroxene (cpx, altered to calcite, ca, and chlorite, ch), in groundmass of plagioclase and K-feldspar, accessory apatite (ap) and opaques. Transmitted plane light, field of view 3.0 mm wide.

RRS08-23 47.3: Possible relict wehrlite (?) composed of talc/sericite (t/s)-possible tremolite-secondary magnetite (opaque) altered relict intercumulus pyroxene (?) sites in matrix of serpentine-magnetite altered relict cumulus olivine (?). Transmitted light, crossed polars, field of view 3.0 mm wide.

RRS08-23 47.3R: Typical relict chromite (ct) partly rimmed and veined by secondary magnetite (mt) and carbonate (cb); magnetite also occurs replacing minute sulfide blebs (mostly pyrrhotite, po) and along discontinuous microveinlets in adjacent silicates (serpentine, serp, and talc/sericite, t/s). Reflected light, uncrossed polars, field of view 2.25 mm wide.

Overview of thin sections and offcuts (green semi-circles mark photomicrograph locations).

PETROGRAPHIC REPORT ON 4 SAMPLES FROM ROSSLAND B.C.

Aug. 24, 2008.

SUMMARY:

Three samples (RRS08-18 6.1, 40.7, 55.8) are variably serpentine-talc/sericite-tremolite-Mg chlorite-magnetite-carbonate altered ultramafic rocks (ranging from wehrlite where least altered to peridotite to undecipherable where most altered). Accessory chromite and minor sulfides (mainly pyrrhotite, minor pentlandite?) are also replaced by magnetite in two samples; in the third, ilmenite appears to have pseudomorphed chromite (?). One sample (RRS08-18 90.2) is biotite-hornblende monzodiorite/monzogabbro. Capsule descriptions are as follows:

RRS08-18 6.1: peridotite (possibly originally wehrlite, if the pyroxene was all clinopyroxene) now extensively altered to talc/sericite-amphibole (late magmatic hornblende, secondary tremolite?)-minor serpentine-secondary magnetite, hosted in intensely fractured, locally sheared, cumulate olivine now partly altered to serpentine-secondary magnetite. Accessory primary euhedral chromite and minute sulfide blebs (pyrrhotite, pyrite/pentlandite?) are also partly altered to magnetite.

RRS08-18 40.7: peridotite (original composition uncertain due to the strong alteration to amphibole (radiating aggregates of tremolite?), serpentine, minor carbonate and secondary magnetite, leaving only small relics of intensely fractured, cumulate olivine). Accessory primary euhedral chromite and minute blebs of sulfide (pyrrhotite, pentlandite?) are also largely altered to secondary magnetite.

RRS08-18 55.8: appears likely to represent a highly altered ultramafic rock, now completely replaced by Mg-chlorite, plus minor carbonate, and trace tremolite (?) along narrow veinlets, with accessory ilmenite likely after former chromite (?).

RRS08-18 90.2: biotite-hornblende monzodiorite/monzogabbro (accessory magnetite-sphene-apatite), partly altered to actinolite-chlorite-calcite-clinozoisite-sericite-rutile in association with narrow planar carbonate-chlorite-plagioclase veinlets.

Detailed petrographic descriptions and photomicrographs are appended (on CD). If you have any questions regarding the petrography, please do not hesitate to contact me.

Craig H.B. Leitch, Ph.D., P. Eng. (250) 653-9158 craig.leitch@gmail.com
492 Isabella Point Road, Salt Spring Island, B.C. Canada V8K 1V4

RRS08-18 6.1: PERIDOTITE (WEHRLITE?): PYROXENE (?) ALTERED TO TALC/SERICITE-AMPHIBOLE, OLIVINE TO SERPENTINE, CHROMITE±SULFIDES TOMAGNETITE

Hand specimen shows dark grey-green to blackish-green, fine-grained, possibly serpentized ultramafic rock, cut by local veinlets also probably mainly of serpentine (?). The rock is partly scratchable by steel, and is strongly magnetic, but shows no reaction to cold dilute HCl, and no stain for K-feldspar in the etched offcut. However, the etching does reveal a cumulate texture, composed mainly of relict olivine, with scattered, fibrous-textured relict pyroxene making up perhaps 15-20% of the sample. Modal mineralogy in polished thin section is approximately:

Olivine (relict)	50%
Talc-sericite (after pyroxene?)	20%
Serpentine (mainly after olivine)	20%
Amphibole (late-magmatic hornblende, after pyroxene?)	3-5%
(secondary tremolite, after pyroxene?)	1-2%
Magnetite (mainly secondary)	2-3%
Chromite (primary, relict)	1-2%
Sulfides (mainly pyrrhotite, possible trace pentlandite or pyrite?)	1%

This sample does represent a strongly altered ultramafic rock, now composed of perhaps 20-25% relict intercumulus pyroxene sites (altered to talc/sericite-late magmatic amphibole-minor tremolite-serpentine-magnetite) hosted in relict cumulate olivine (altered to serpentine-secondary magnetite) and accessory chromite and sulfides (rimmed/altered to secondary magnetite).

Olivine, originally forming irregular subhedral crystals up to about 3 mm in maximum dimension, is intensely fractured and in part altered to serpentine-secondary magnetite along these fractures, which are commonly spaced <0.1 mm apart. Locally, the olivine is sheared in zones up to 1.5 mm thick. Microveinlets of secondary magnetite, mostly <50 microns thick, composed of interlocking minute subhedral crystals of magnetite mostly <15 microns in size, are spaced approximately 0.5-1.0 mm apart, and are typically associated with or surrounded by more abundant serpentine envelopes up to 0.5 mm thick, in which serpentine forms sub/euhedral flakes up to about 0.1 mm diameter.

Relict pyroxene (?) sites have irregular, glomeratic subhedral outlines up to about 7 mm across, with a pronounced lamellar structure preserved in them by alignment of narrow (<0.5 mm) ribbons of medium brown amphibole (likely late-magmatic hornblende?) as granular aggregates of rounded, <1 mm long subhedra, locally surrounded by aligned euhedral bladed laths of colourless amphibole (tremolite?) <0.2 mm long. The host to the amphibole ribbons is more or less sub-parallel aligned, fine-grained talc/sericite (most likely talc) as sub/euhedral flakes <0.1 mm in diameter. Locally, minor serpentine is mixed with the talc, and minute sub- to euhedral crystals of secondary magnetite, mostly <50 microns in diameter, are common, particularly in the amphibole ribbons.

Accessory primary chromite, forming mainly euhedral crystals up to 2 mm (locally skeletal, glomeratic aggregates up to 4 mm) is generally rimmed and partly replaced along microveinlets by secondary magnetite and minor sulfides (both mostly <25 microns in size). Separate blebs of likely primary sulfides (in interstitial positions between serpentized olivine relics) are rarely over about 0.1 mm in diameter, making identifications difficult. However, they appear to comprise mostly pyrrhotite (?) as interlocking subhedra <50 microns in size, and lesser white, harder sulfide (possibly pyrite or pentlandite, if there are Ni values), both locally cut by microveinlets of secondary magnetite <5 microns thick.

In summary, this appears to represent peridotite (possibly originally wehrlite, if the pyroxene was all clinopyroxene) now extensively altered to talc/sericite-amphibole (late magmatic hornblende, secondary tremolite?)-minor serpentine-secondary magnetite, hosted in intensely fractured, locally sheared, cumulate olivine now partly altered to serpentine-secondary magnetite. Accessory primary

euhedral chromite and minute blebs of sulfide (pyrrhotite, pyrite/pentlandite?) are also partly altered to secondary magnetite.

RRS08-18 40.7: STRONGLY TREMOLITE-SERPENTINE-CARBONATE-MAGNETITE ALTERED ULTRAMAFIC ROCK (PERIDOTITE?); ACCESSORY CHROMITE, TRACE SULFIDES ALSO REPLACED BY MAGNETITE

Hand specimen shows dark grey-green mottled-looking, fine-grained, possibly serpentinized ultramafic rock, cut by local dark veinlets, also probably mainly of serpentine (?). The rock is partly scratchable by steel, and is strongly magnetic, shows minor reaction to cold dilute HCl, and no stain for K-feldspar in the etched offcut. However, the etching does suggest relict cumulate texture, composed mainly of relict olivine (?). Modal mineralogy in polished thin section is approximately:

Amphibole (secondary tremolite, after pyroxene?)	45%
Serpentine (mainly after olivine)	25%
Olivine (relict)	20%
Carbonate (partly calcite, dolomite/magnesite?)	5%
Magnetite (mainly secondary)	2-3%
Chromite (primary, relict)	1-2%
Sulfides (mainly pyrrhotite, possible trace pentlandite or pyrite?)	1%

This sample appears to represent a strongly altered ultramafic rock, now composed of irregular aggregates of tremolite-serpentine-minor magnetite (locally with carbonate), commonly with a reticulate texture, in which only minor relict cumulate olivine, and accessory chromite and sulfides (rimmed/altered to secondary magnetite) are preserved.

Olivine, originally forming irregular subhedral crystals possibly as much as 3 mm in maximum dimension, is preserved only as intensely fractured relicts <0.5 mm across, largely altered to serpentine-secondary magnetite along these fractures, which are commonly spaced <50 microns apart. The relicts are enclosed in a matrix of serpentine and colourless amphibole which could represent more altered olivine, or possibly pyroxene (not possible to tell). Microveinlets of secondary magnetite, mostly <0.25 mm thick, composed of interlocking minute subhedral crystals of magnetite mostly <65 microns in size, are spaced approximately 1-2 mm apart in some zones, and are commonly associated with or surrounded by envelopes up to 0.5 mm thick, in which tremolite and carbonate are more abundant. Serpentine forms sub/euhedral flakes up to about 0.2 mm diameter that vary from pale yellowish to greyish (possibly two different varieties/stages of serpentinization). Amphibole is likely the Mg-rich end member tremolite (lacks colour, has small extinction angle <13 degrees, and forms radiating aggregates of fibrous lath-shaped crystals mostly <0.5 mm long). Carbonate may include both calcite moderate reaction to cold dilute HCl in hand specimen) and dolomite or magnesite, forming irregular aggregates up to about 2 mm across composed of interlocking subhedra mostly <0.65 mm in diameter.

Accessory primary chromite, forming sub/euhedral crystals up to 1 mm (in part as skeletal, glomeratic aggregates up to 2 mm) is heavily rimmed and replaced by secondary magnetite (mostly <50 microns in size). Separate blebs of likely primary sulfides (in interstitial positions between serpentine-tremolite altered relicts) are rarely over about 0.1 mm in diameter, making identifications difficult. However, they appear to comprise mostly pale brownish pyrrhotite (?) as interlocking subhedra up to 65 microns in size, with minor "flames" of white, harder sulfide (possibly pentlandite, if Ni values are elevated). Both sulfides are locally 30-70% replaced by secondary magnetite as sub/euhedra <50 microns in diameter.

In summary, this appears to represent peridotite (not possible to tell what the original composition was due to the strong alteration to amphibole (radiating aggregates of tremolite?), serpentine, minor carbonate and secondary magnetite, leaving only small relicts of intensely fractured, cumulate olivine). Accessory primary euhedral chromite and minute blebs of sulfide (pyrrhotite, pentlandite?) are also largely altered to secondary magnetite.

RRS08-18 55.8: COMPLETELY MG CHLORITE-MINOR CARBONATE-TREMOLITE?
ALTERED ULTRAMAFIC ROCK (ACCESSORY ILMENITE AFTER CHROMITE)

Hand specimen shows a dark grey-green, very fine-grained (intensely serpentinized/altere?) ultramafic rock in which little original texture remains visible, even in the etched offcut; it is cut by narrow planar paler-coloured fractures. The rock is only weakly magnetic, shows no reaction to cold dilute HCl (even after powdering, or even in the fractures), and no stain for K-feldspar in the etched offcut. Modal mineralogy in polished thin section is approximately:

Mg-chlorite (after olivine?)	95%
Ilmenite (after chromite?)	2-3%
Carbonate (magnesite?)	1-2%
Tremolite or talc/sericite (?)	<1%
Magnetite (secondary?)	<1%

This is an intensely altered rock, essentially lacking any relict primary texture, and in which the mineralogy is very simple (virtually entirely magnesian chlorite, except in and along narrow planar veinlets of carbonate and minor tremolitic amphibole?). Accessory opaque oxides are mainly ilmenite, with only traces of secondary magnetite (along the veinlets); there are no sulfides visible.

Chlorite forms massive replacements of the original rock, as mainly randomly oriented to locally radiating, scaly, subhedral flakes up to about 0.25 mm in diameter, but commonly < 0.1 mm. In places the chlorite is partly plucked out, likely due to section preparation. Optical characteristics (colourless, distinctive length-fast, first-order white birefringence) indicate a magnesian composition for the chlorite, with Fe:Fe+Mg, or F:M, ratio probably around 0.3. This magnesian composition reinforces the hypothesis that the sample represents an intensely altered ultramafic rock.

Disseminated opaque oxides, forming aggregates mostly <0.6 mm in diameter composed of sub/euhedral tabular to lath-shaped crystals mostly <0.25 mm in size, are mainly ilmenite (likely after former primary chromite?).

Along the planar veinlets, which are mainly <0.5 mm thick, carbonate (likely magnesite since it shows no reaction to cold dilute HCl, even when powdered) forms interlocking subhedra mostly <0.25 mm long, commonly aligned along the veinlet. Some of the veinlets are open. In the immediately adjacent envelope, minor amounts of a pale brownish to colourless mineral forming bladed, lath-like subhedra mostly <0.1 mm long is tentatively identified as amphibole (tremolite?) or talc/sericite (?). Minor amounts of secondary magnetite (forming subhedra mostly <20 microns) are associated with or found within these veinlets, mainly partly replacing ilmenite in or adjacent to the veinlets.

In summary, this appears likely to represent a highly altered ultramafic rock, now completely replaced by Mg-chlorite, plus minor carbonate, and trace tremolite (?) along narrow veinlets, with accessory ilmenite likely after former chromite (?).

RRS08-18 90.2: PORPHYRITIC BIOTITE-HORNBLENDE MONZODIORITE/MONZOGABBRO
ALTERED TO ACTINOLITE-CHLORITE-CALCITE-EPIDOTE-SERICITE-RUTILE

Hand specimen shows a dark grey-green, altered-looking, relatively fine-grained plutonic rock in which the texture is obscured by the alteration; it is possibly too siliceous (harder than steel) for a serpentinized ultramafic. The rock is magnetic, shows minor reaction to cold dilute HCl, and weak yellow stain for K-feldspar in the etched offcut (mainly in the groundmass of what is revealed to be a porphyritic rock characterized by 10-20% 2-3 mm dark mafic phenocrysts). Modal mineralogy in thin section is approximately:

Amphibole (phenocrysts and groundmass; actinolitic?)	40%	
Plagioclase (andesine-labradorite?)		35%
K-feldspar (primary, groundmass)		10%
Biotite (partly chloritized)		5%
Chlorite	3%	
Carbonate (mainly calcite?)		2%
Opaque (mainly magnetite?)		1%
Epidote (clinozoisite?)	1%	
Sericite	1%	
Sphene, trace rutile		1%
Apatite		<1%

This sample consists mainly of about 15-20% phenocrysts of amphibole plus minor biotite, set in a finely crystalline groundmass of plagioclase, partly chlorite-carbonate-epidote altered amphibole and minor biotite, lesser K-feldspar, carbonate, opaque oxides, and sphene.

Amphibole phenocrysts have mainly euhedral outlines up to about 2 mm (3 mm where glomeratic, with biotite). The amphibole is generally pale green, with small extinction angle about 15 degrees and fibrous habit (lath-shaped crystals rarely over about 1 mm long), suggestive of actinolite (?). In some of the aggregates, the fringes of individual amphibole crystals are partly altered to minute flakes of pale brown secondary biotite mostly <30 microns in diameter, or are the cores are replaced by ragged subhedra of epidote-group mineral up to 0.5 mm in size.

Biotite phenocrysts have mainly euhedral outlines up to 1.25 mm in diameter, with pale to medium brown pleochroism and generally rimmed or partly replaced by chlorite (distinct green pleochroism, near-zero birefringence indicative of F:M around 0.5?) accompanied by minute crystals of sagenitic rutile, and small euhedral prisms of apatite up to 0.15 mm long. Microphenocrysts of sphene, separate from or associated with biotite, have sub/euhedral outlines up to 0.5 mm.

In the groundmass, plagioclase forms interlocking, randomly oriented, mainly euhedral lath- to tablet-shaped crystals <0.6 mm long that are generally only slightly altered to minute (<25 micron) flakes of sericite. The crystals typically show compositional zoning, particularly around the rims, with composition varying from cores of about andesine-labradorite (An₅₀, based on extinction on 010 up to 30 degrees) to narrow more sodic rims. Most K-feldspar forms much finer-grained material, interstitial to or surrounding the plagioclase. Lath-like amphibole (also likely actinolitic) and lesser flakes of pale brown biotite mostly <0.4 and <0.2 mm in diameter are both partly altered to chlorite, carbonate, epidote-group mineral, and associated with very fine-grained sphene and opaques mostly <25 microns. Carbonate is likely mainly calcite, forming aggregates mostly <0.1 mm across of interlocking <30 micron subhedra. Epidote-group mineral forms ragged subhedra <0.1 mm in size, with slightly anomalous birefringence and lacking pleochroism, indicative of an Fe-poor composition (clinozoisite). Narrow veinlets <0.15 mm thick are filled with carbonate, chlorite and sodic plagioclase all mostly <0.1 mm long.

In summary, this would be classed as biotite-hornblende monzodiorite/monzogabbro (accessory magnetite-sphene-apatite), partly altered to actinolite-chlorite-calcite-clinozoisite-sericite-rutile in association with narrow planar carbonate-chlorite-plagioclase veinlets.

PHOTOMICROGRAPH CAPTIONS

RRS08-18 6.1: Relict peridotite (wehrlite?) composed of talc/sericite (t/s)-amphibole (am)-secondary magnetite (opaque) altered pyroxene relics hosted in highly fractured olivine (ol) partly altered to serpentine (serp) and microveinlets of secondary magnetite. Transmitted light, crossed polars, field of view 3.0 mm wide.

RRS08-18 6.1R: Overview to show relict primary chromite (ct) crystals rimmed and veined by secondary magnetite (mt), and small blebs of sulfide (sx) interstitial to highly fractured and locally sheared olivine (ol), with replacement by secondary magnetite along discontinuous microveinlets. Reflected light, uncrossed polars, field of view 2.75 mm wide.

RRS08-18 6.1R2: Detail of sulfide blebs composed of brownish pyrrhotite (po) and white pyrite or pentlandite? (py/pn?), both cut by minute microveinlets of secondary magnetite (mt) that is also associated with serpentine (serp) after fractured olivine (ol). Reflected light, uncrossed polars, field of view 1.0 mm wide.

RRS08-18 40.7: Intensely altered peridotite now composed of radiating tremolite (tr), serpentine (serp), local carbonate (cb) with only minor relict olivine (ol), and secondary magnetite (mt) locally partly after relict primary chromite (ct). Transmitted light, crossed polars, field of view 3.0 mm wide.

RRS08-18 40.7R: Detail of sulfide blebs composed of brownish pyrrhotite (po) and minute “flames” of white pentlandite? (pn?), heavily replaced by secondary magnetite (mt) that is also associated with serpentine (serp)-tremolite (tr)-carbonate (cb) after fractured olivine (ol). Reflected light, uncrossed polars, field of view 1.0 mm wide.

RRS08-18 55.8 Relict ultramafic rock (?) now composed almost entirely of subhedral flakes of Mg-chlorite (ch) with random/radiating orientations, containing disseminated ilmenite (il) and cut by narrow planar veinlets of carbonate (cb, possibly magnesite?), local tremolite (tr?), trace magnetite (mt). Transmitted light, partly crossed polars, 3.0 mm wide.

RRS08-18 55.8R: Approximately same area, to show fine-grained aggregates of ilmenite (il), commonly recrystallized (rexst) to bladed laths near veinlets, or partly replaced by traces of magnetite (mt). Reflected light, uncrossed polars, field of view 2.25 mm wide.

RRS08-18 90.2: Phenocrysts of actinolitic amphibole (am) and biotite (bi, partly chloritized at rims), rare sphene (sp) associated with opaque oxides, in groundmass of plagioclase (minor K-feldspar), needle-like amphibole, biotite, minor carbonate (ca), sphene and opaques. Transmitted plane light, field of view 3.0 mm wide.

Overview of thin sections and offcuts (green semi-circles mark photomicrograph locations).

PETROGRAPHIC REPORT ON 2 SAMPLES FROM ULTRAMAFIC ROCK EXPOSURES,
ROSSLAND B.C.

SUMMARY:

The two samples are taken from an outcrop described as olivine wehrlite, locally wehrlite with trace to several percent chromite (Record Ridge ultramafic body, BCGS Bulletin 108). In thin section, they are characterized as variably serpentinized ($\pm$ talc/sericite-muscovite, secondary magnetite, minor tremolite?, carbonate altered) ultramafic rocks, possibly peridotite of original wehrlite or lherzolite (?) composition (accessory chromite, magnetite, trace sulfide). Capsule descriptions are as follows:

RRS-Trench: appears to represent a peridotite (possibly wehrlite?) composed of serpentine-secondary magnetite (mainly after former olivine, relicts of which remain) and lesser talc/muscovite, minor carbonate, trace secondary magnetite (possibly after subordinate pyroxene), plus accessory relict primary chromite, trace very fine-grained sulfides.

Upper outcrop: peridotite (lherzolite?) composed of fractured olivine partly altered to serpentine-secondary magnetite and lesser talc/sericite, minor carbonate, with areas (possibly after subordinate pyroxene?) now composed of muscovite-talc/sericite-minor amphibole or relict orthopyroxene (?), plus traces of relict primary chromite (replaced by secondary magnetite) and very fine-grained sulfides. Vein-like areas of more intense talc/sericite-carbonate-magnetite alteration cut the sample.

Detailed petrographic descriptions and photomicrographs are appended (by email attachment). If you have any questions regarding the petrography, please do not hesitate to contact me.

Craig H.B. Leitch, Ph.D., P. Eng. (250) 653-9158 craig.leitch@gmail.com
492 Isabella Point Road, Salt Spring Island, B.C. Canada V8K 1V4

RRS Trench: RELICT WEHLITE (?) ALTERED TO SERPENTINE-TALC/MUSCOVITE-MAGNETITE-MINOR CARBONATE; ACCESSORY CHROMITE, TRACE SULFIDE

Hand specimen shows fine-grained, dark blackish green, somewhat mottled ultramafic rock (mottling caused by irregular network-like paler coloured areas that could be amphibole or mica?). The rock is strongly magnetic, but shows no reaction to cold dilute HCl, and no stain for K-feldspar in the etched offcut. Modal mineralogy in polished thin section is approximately:

Serpentine (after olivine?)	55%
Mica (talc or muscovite?)	25%
Relict olivine (?)	10%
Magnetite (largely secondary)	7-8%
Chromite (primary?)	1-2%
Carbonate (magnesite?)	1%
Sulfide (pyrite or pyrrhotite?)	trace

This sample consists mainly of very fine-grained serpentine-secondary magnetite pseudomorphs (likely mainly after olivine, minor relicts of which remain) with network-like patches of coarser-grained mica (talc or muscovite?) locally mixed with minor carbonate, lesser secondary magnetite. Scattered chromite crystals with euhedral outlines up to 0.5 mm in diameter are likely primary (most are rimmed or partly replaced by secondary magnetite). Traces of minute sulfides (aggregates <40 microns of mostly <15 micron crystals) are too fine-grained to identify properly; they could be pyrite or pyrrhotite.

Serpentine forms randomly oriented, interlocking, subhedral flakes mostly <0.1 mm in diameter (commonly <50 microns). They vary from relatively clear, very pale yellowish green, to cloudy grey, or locally opaque due to varying amounts of almost amorphous, minute (<3 microns) to crystalline (sub/euhedral, 10-35 micron) crystals of secondary magnetite. Loosely defined aggregates of this secondary magnetite up to 0.3 mm across are common. Relict texture indicates that most of the serpentine/magnetite is likely after former olivine crystals mainly <0.25 mm in diameter, with a fine-grained cumulate texture. This is supported by the presence locally of rounded, subhedral, olivine relict crystals up to 0.2 mm in diameter, commonly partly clouded by incipient brownish alteration that may be iddingsite (?). It is possible that some of the olivine crystals originally were up to as much as 0.5 or even 1 mm across, but all that remains are fractured remnants.

The mica occurs in loosely defined, ragged irregular patches up to about 3 mm across, composed of sub to euhedral flakes or locally radiating sprays up to 1 mm in diameter. Although talc is indistinguishable from muscovite (sericite) optically, the generally high birefringence and association with ultramafic rock suggests it is likely to be talc. Locally the mica is mixed with minor amounts of carbonate as interlocking sub/anhedral crystals mostly <0.15 mm in size, but joined in networks interstitial to the serpentinized olivine that are optically continuous for up to 1.5 mm across. Much lesser amounts of minute to microcrystalline secondary magnetite are associated with the mica-rich areas. It is not certain what these minerals are pseudomorphous after, but since they are different from the olivine, pyroxene (possibly clinopyroxene) is likely. If so, this would suggest an original wehrlite composed of about 25-30% pyroxene and 70% olivine, with accessory chromite.

In summary, this appears to represent a peridotite (possibly wehrlite?) composed of serpentine-secondary magnetite (mainly after former olivine, relicts of which remain) and lesser talc/muscovite, minor carbonate, trace secondary magnetite (possibly after subordinate pyroxene), plus accessory relict primary chromite, trace very fine-grained sulfides.

Upper outcrop: RELICT LHERZOLITE (?) ALTERED TO SERPENTINE-TALC/MUSCOVITE-MAGNETITE-MINOR AMPHIBOLE-CARBONATE; TRACE RELICT CHROMITE, SULFIDE

Hand specimen shows mottled-looking ultramafic rock (composed of fine-grained, dark blackish green matrix with patches/aggregates of slightly paler coloured coarse crystals that could be pyroxene relics?). The rock is strongly magnetic, but shows no reaction to cold dilute HCl, and no stain for K-feldspar in the etched offcut. Modal mineralogy in polished thin section is approximately:


Relict olivine (?)	55%
Muscovite	20%
Serpentine (after olivine?)	10%
Talc/sericite	10%
Magnetite (largely secondary)	2-3%
Amphibole (tremolite?)	1-2%
Carbonate (magnesite?)	1%
Sulfide (pyrite or pyrrhotite?)	trace

This sample consists mainly of strongly fractured, relatively fine-grained olivine (partly altered to fine-grained serpentine-secondary magnetite, with patches of coarse-grained muscovite/fine-grained talc/sericite, possibly after colourless amphibole (which may in turn be after former pyroxene?), all cut by veinlet-like areas talc/sericite-secondary magnetite-carbonate. Rare aggregates of magnetite with euhedral outlines up to 0.5 mm in diameter likely represent primary chromite crystals replaced by secondary magnetite. Traces of minute sulfides (aggregates <0.1 mm across of mostly <15 micron crystals) are too fine-grained to identify properly, but could be pyrite or pyrrhotite.


Olivine forms somewhat rounded, sub/euhedral crystals mostly <1 mm in diameter (locally optically continuous for up to 2 mm), but highly fractured into small sub-domains mostly <0.2 mm in size, and locally partly clouded by incipient brownish alteration that may be iddingsite (?). Serpentine alteration is mainly restricted to the fractures, where it forms commonly aligned, subhedral flakes mostly <0.2 mm in diameter. The serpentine is relatively clear to very pale yellowish green, and is locally associated with talc/sericite as mainly euhedral flakes <0.25 mm in diameter and varying amounts of microcrystalline (sub/euhedral, 10-35 micron) crystals of secondary magnetite. Loosely defined aggregates of this secondary magnetite up to 0.1 mm are present along narrow anastomosing veinlets.

The coarse mica occurs in loosely defined, ragged irregular patches up to about 4 mm across, composed of sub to euhedral flakes or locally radiating sprays up to 2 mm in diameter. It could be either talc or muscovite; the large flakes are locally altered along margins to flakes of talc/sericite as described above, which seems to be pseudomorphing them. Local crystals of colourless amphibole (with very small extinction angle, possibly tremolite, or less likely orthopyroxene?) have sub- to euhedral outlines up to 2.5 mm. Locally the mica is mixed with minor amounts of carbonate as interlocking sub/anhedral crystals mostly <0.15 mm in size, but joined in networks interstitial to the serpentinized olivine that are optically continuous for up to 1 mm; lack of reaction to HCl suggests it may be magnesite (?). It is not certain what these minerals are pseudomorphous after, but since they are different from the olivine, pyroxene (possibly with some orthopyroxene) is likely; if so, this would suggest an original lherzolite, composed of about 30% pyroxene and 70% olivine plus trace chromite (?).


In summary, this appears to represent a peridotite (possibly lherzolite?) composed of fractured olivine partly altered to serpentine-secondary magnetite and lesser talc/sericite, minor carbonate, with areas (possibly after subordinate pyroxene?) now composed of muscovite-talc/sericite-minor amphibole or relict orthopyroxene (?), plus traces of relict primary chromite (replaced by secondary magnetite) and very fine-grained sulfides. Vein-like areas of more intense talc/sericite-carbonate-magnetite alteration cut the sample.

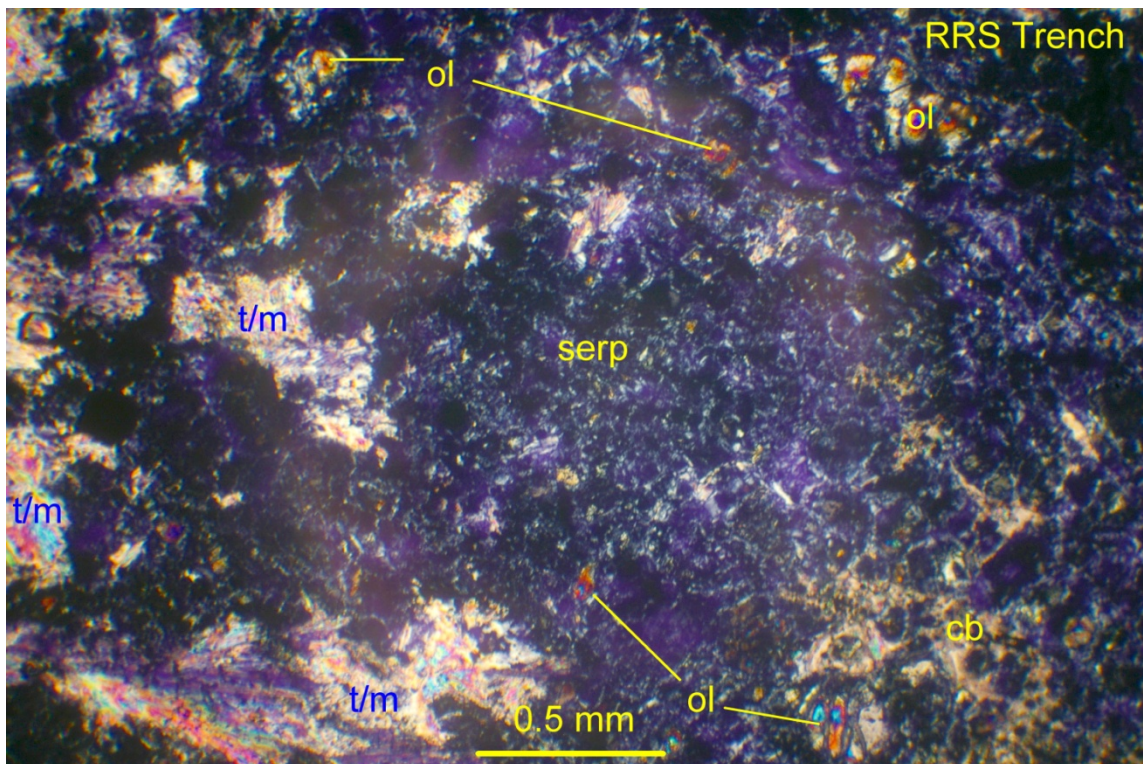


RRS Trench: Serpentinized wehrlite (?) composed of talc/muscovite (t/m), minor carbonate (cb) altered relict pyroxene (?) sites in a matrix of dark, serpentine-secondary magnetite altered relict olivine sites (minor small relict remnant olivine, ol). Transmitted light, crossed polars, field of view 3.0 mm wide.

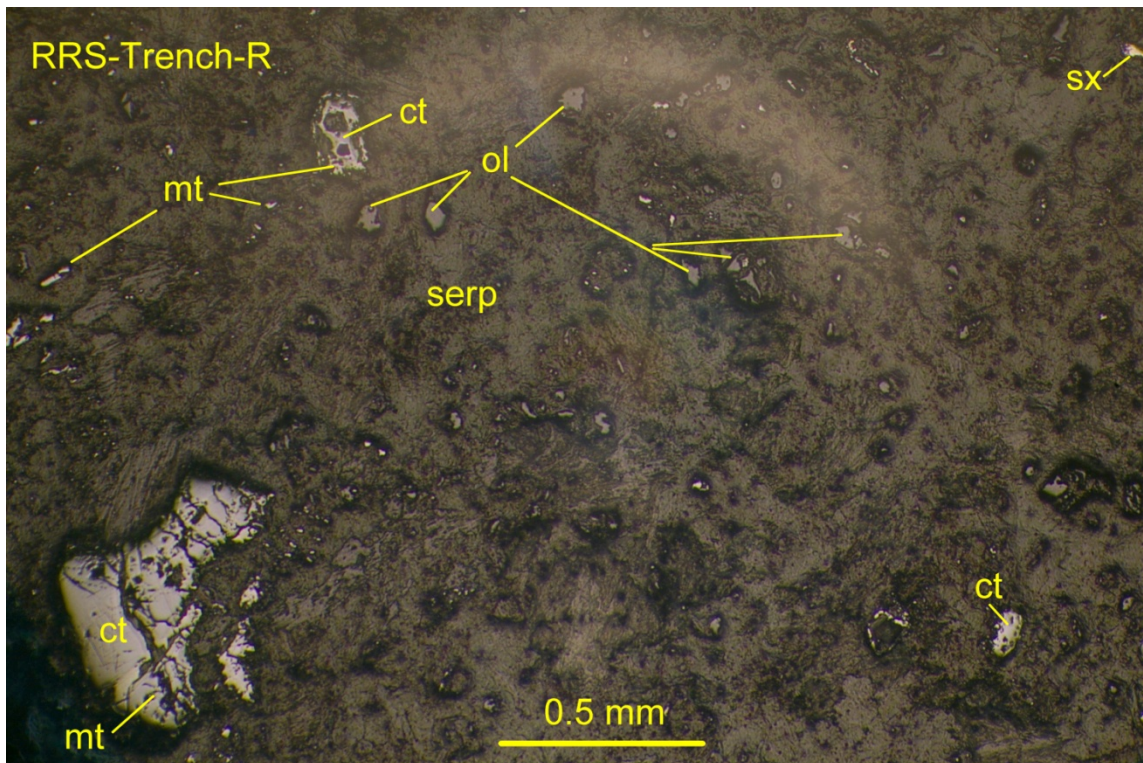

RRS Trench-R: Relict primary chromite (ct) crystals partly rimmed or replaced by magnetite (mt) that also occurs with serpentine replacing matrix olivine (?). Traces of sulfide (sx) are rarely visible. Reflected light, uncrossed polars, field of view 2.75 mm wide.

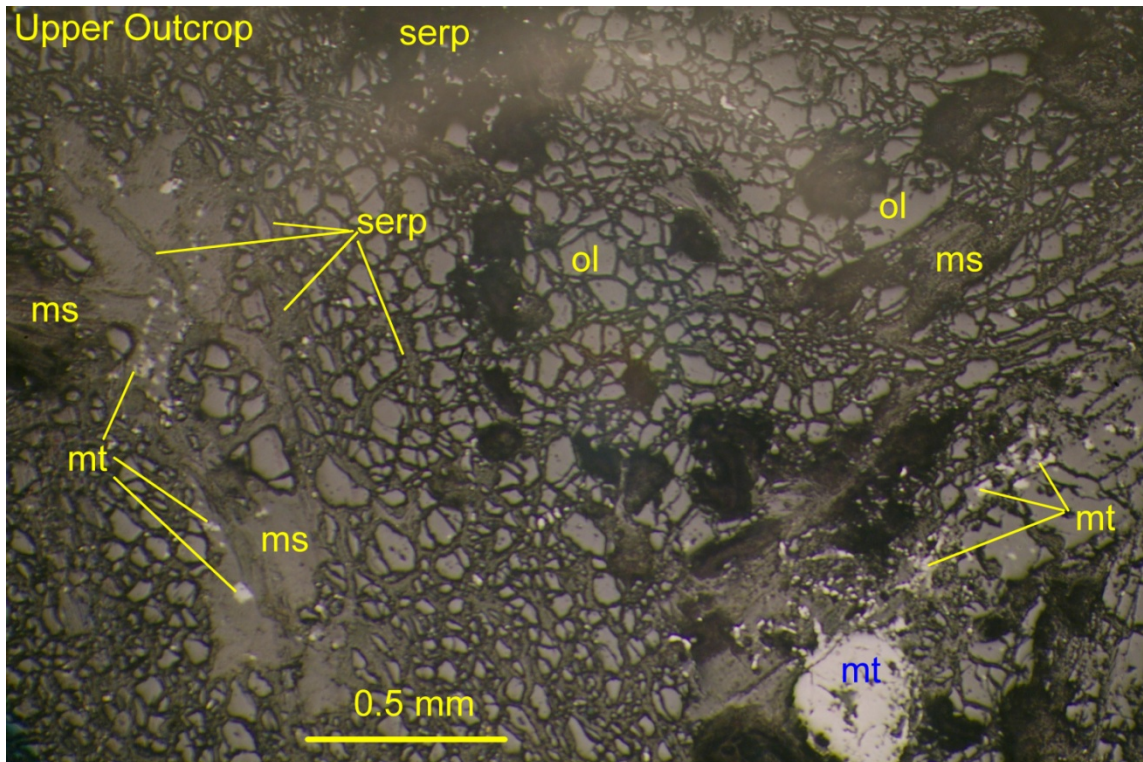

Upper Outcrop: relict peridotite composed of highly fractured olivine (ol) altered to serpentine (serp), plus bladed relicts of possible pyroxene (?) replaced by muscovite (ms). Both the silicates and possible relict chromite are replaced by secondary magnetite (mt). Reflected light, uncrossed polars, field of view 2.75 mm wide.

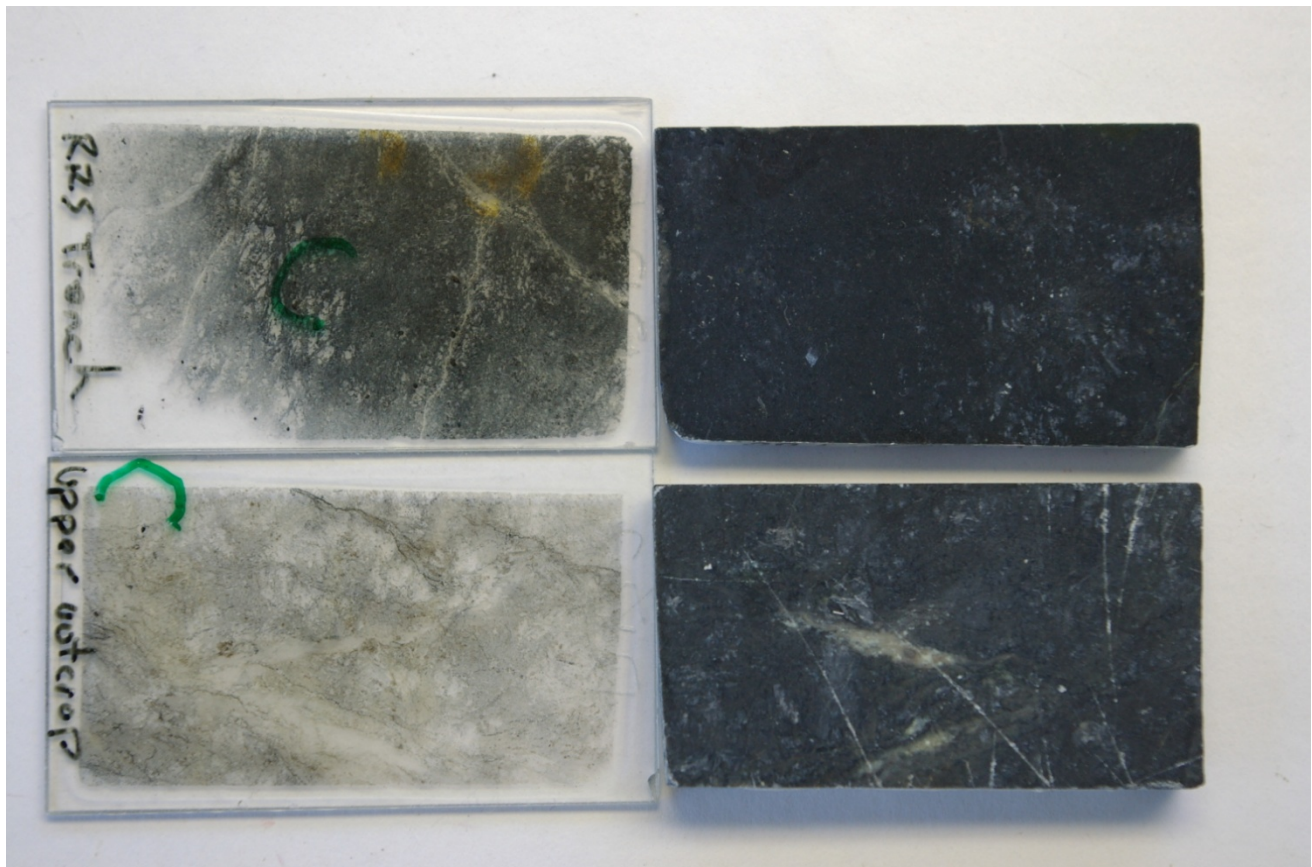

Overview of thin sections and offcuts (green semi-circles mark photomicrograph locations).