

Assessment Report

**BC Geological Survey
Assessment Report
32560**

**Diamond Drilling
on the
Bing Property
(Formerly the Icy Lake Property)**

Atlin Mining Division

104K/08

**UTM Zone 08 NAD83
664000E 6474000N**

**58⁰ 22' North Latitude
132⁰ 12' West Longitude**

For

Paget Minerals Corp.

By

David Volkert

October 2011

Table of Contents

Introduction.....	3
Location and Access.....	3
Physiography, Climate and Vegetation	3
Claims and Ownership	4
Exploration History	7
Regional Geological Setting	8
Property Geology	10
Mineralization and Alteration	10
<i>Bing</i>	10
Work Completed 2011	12
Diamond Drilling	12
<i>PB-11-01 – Moly Creek</i>	16
<i>PB-11-02 – Chalco Creek</i>	16
<i>PB-11-03 – South Zone</i>	17
Conclusions and Recommendations.....	17
<i>Bing</i>	17
References.....	18
Appendix A: Statement of Qualifications.....	20
Appendix B: Statement of Costs	21
Appendix C: Cross Sections	22
Appendix D: Core Logs.....	29
<i>BC-11-01</i>	29
<i>BC-11-02</i>	42
<i>BC-11-03</i>	53
Appendix E: Analytical Certificates.....	61

List of Figures

Figure 1	Location Map
Figure 2	Claim Map
Figure 3	Regional Geology
Figure 4	Drill Hole Locations (1:50,000)

List of Tables

Table 1	Claim Status
Table 2	Historical exploration work in the Icy Lake Property area
Table 3	Diamond Drill Hole Locations
Table 4	Notable Diamond Drill Intercepts

Diamond Drilling on the Bing Property

Introduction

The Bing Property was examined by the author and geologists Jim Ashleman, Chris Weldon, Eric Alexander and Kayla Dell from June 1st to August 1st, 2011. The area, previously known as the Icy Lake Property, has been renamed the Bing Property as most of the Icy Lake claims have been dropped and exploration is now focused on the Bing claims. The purpose of the visit was to evaluate the economic potential of the claims by a diamond drilling program on previously determined targets. A 1005.8m drill program consisting of three diamond drill holes was completed on the eastern side of the Bing Porphyry during Summer 2011. All work including report writing was completed at a cost of \$1,001,951.63

Location and Access

The Bing Property is located in northwestern B.C. about 100 kilometers northwest of Telegraph Creek and 125 kilometers west of Dease Lake (Figure 1). The property is located in NTS 104K/08, latitude 58°22'N, longitude 132°12'W. Formerly road access to within about 11 kilometers of the southern property boundary was provided by the Golden Bear mine access road, which is presently not usable due to landslides and washouts. From the Golden Bear road access could be easily constructed to the southeastern part of the property along the Samatua River drainage. Work on the property during the 2011 program was helicopter-based from the Shelsay hunting camp operated by the Day Brothers of the Tahltan First Nation. Camp mobilization was facilitated by use of fixed wing access from Dease Lake to the Sheslay air strip, located at the junction of the Sheslay and Hackett Rivers, 22 kilometers southeast of the property.

Physiography, Climate and Vegetation

Elevations range from 800 meters in the western part of the property at Tatsamenie Lake, to 1900 meters in the central part of the property. The area is characterized by high relief and steep slopes, and topography is rugged, with prominent ridges rising above glaciated U-shaped valleys. Climate is typical of the interior parts of northern B.C. with moderate snowfalls, long, cold winters and short cool summers. The upper slopes and ridges of the property are typical alpine terrain, characterized by grassy meadows on flatter ridges, rock and talus-strewn slopes in steeper areas. The lower parts of the property (below 1400-1500 meters) are characterized by moderate to dense vegetation including cedar, fir, spruce, and aspen.

Claims and Ownership

The Bing Property, formerly known as the Icy Lake property consists of 6 contiguous claims which total 848.9 hectares, as indicated on Figure 2. The name of the claim blocks was changed from Icy Lake to Bing in 2011 when the number of claim blocks was reduced from 17 to 6 and the Icy Lake claims were discarded. The current claim tenures focus on the Bing property. They are owned 100% by Paget Minerals Corp. (BCE ID number 213190) of 1210-1130 W. Pender St., Vancouver, BC. The claims are currently valid until November 1, 2014.

Table 1 Claim Status

Tenure Number	Claim Name	Owner	Good To Date	Status	Area
549122	BING TOP	213190 (100%)	2014/Nov 01	GOOD	271.700
549125	TAT2	213190 (100%)	2014/Nov 01	GOOD	84.893
549130	BING CHERRY	213190 (100%)	2014/Nov 01	GOOD	135.803
549156	MC HAMMER	213190 (100%)	2014/Nov 01	GOOD	84.863
549157	ICY LAKE 2	213190 (100%)	2014/Nov 01	GOOD	101.915
549674	WOLFMOTHER	213190 (100%)	2014/Nov 01	GOOD	169.761
Total					848.935



Figure 1: Location Map

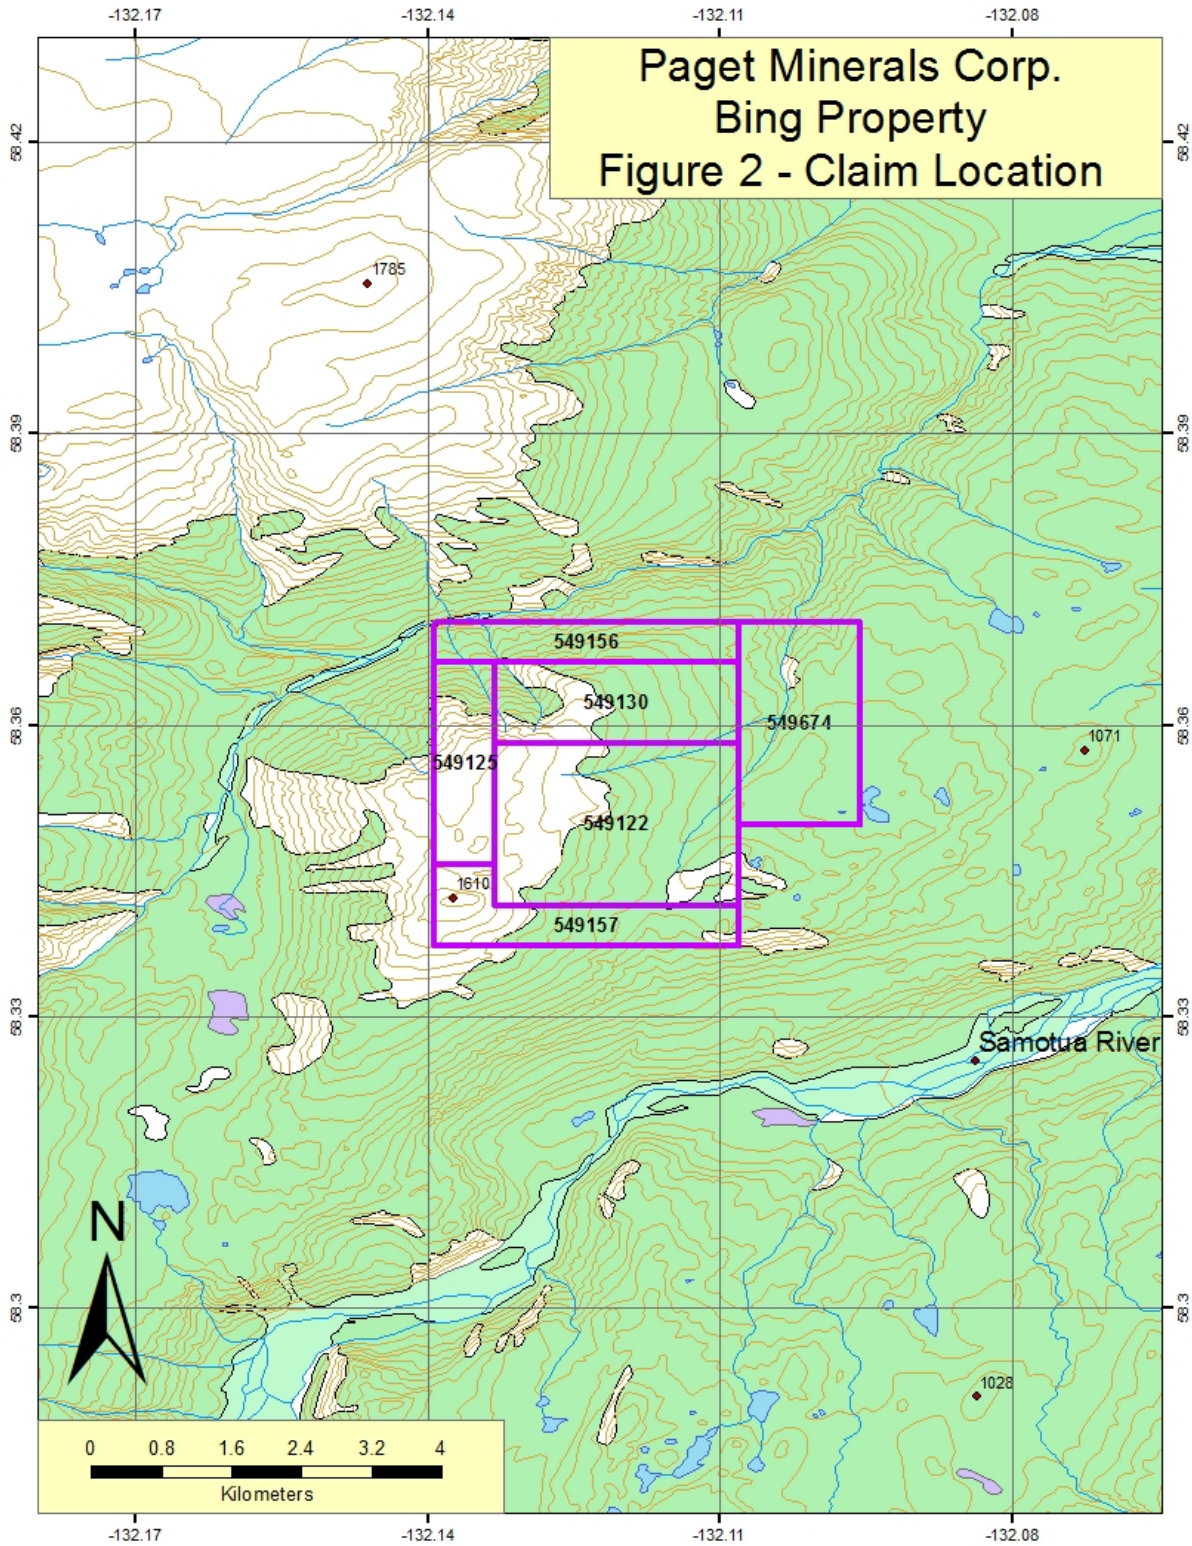


Figure 2: Claim Map

Exploration History

The Tatsamenie Lake area has been explored sporadically by numerous companies since early exploration of the Bing porphyry system by Newmont in 1964-1966. Exploration in the area of the Icy Lake Property is documented in nine assessment reports available on the B.C. Ministry of Mines ARIS website (<http://www.em.gov.bc.ca/cf/aris/>). In 1971, Souther published a 1:250,000 scale regional map of the Tulsequah map area which outlined a large alteration zone extending from the west side of Tatsamenie Lake to the Bing area, a distance of over 20 kilometers (Souther, 1971). The Icy Lake (MC or Ant) porphyry was identified initially by V. Cukor and P.H. Sevensma in 1970 for the Colorado Corporation; it was subsequently worked by Skyline Exploration and Brinex in 1971, and by Rio Tinto in 1976-1977. Discovery of the Golden Bear gold deposit in the 1980's spurred a renewed look at the area by Chevron and North American Metals as well as a number of junior exploration companies.

Table 2 Historical exploration work in the Icy Lake Property area.

Report #	Year Work Done	Company	Work Done
653	1965	Newmont	Geological mapping
668	1965	Newmont	Ground and airborne magnetics, IP, soil sampling (789 samples), geological mapping
3075	1970	Colorado Corp.	Geological mapping, soil sampling (318 samples), rock sampling (18 samples)
3475	1971	Brinex/Skyline	Geological mapping, trenching, soil and silt sampling (227 samples), rock sampling (84 samples)
6019	1976	Rio Tinto	Geological mapping, trenching, soil sampling (298 samples), rock sampling (84 samples)
21987	1990	Waterford Res.	Geological mapping, rock sampling (315 samples), ground VLF/mag
23431	1993	Allan Res.	Trenching, rock sampling, ground EM/mag
23554	1994	Tahltan Holdings	Soil sampling (66 samples)

25150	1996	Premier Minerals/Inukshuk Capital	Geological mapping, rock and soil sampling
29345	2007	Paget Resources Corporation	Geologic mapping, rock sampling (83 samples)

Regional Geological Setting

The Icy Lake Property is located within northern Stikine Terrane, which comprises a series of mid-Paleozoic to Middle Jurassic volcano-plutonic arc sequences west of oceanic rocks of the Cache Creek Terrane. Paleozoic basement rocks are informally known as Stikine Assemblage. A prominent Permian limestone unit cores a series of structural culminations in the area and is structurally overlain by Carboniferous felsic to mafic volcanics (Figure 3).

The Paleozoic supracrustal rocks are intruded by voluminous diorite to quartz diorite plutons of Middle to Late Triassic age. These plutons have a widely developed structural fabric not found in more felsic Jurassic to Eocene intrusive rocks. Except in the southeastern part of the Icy Lake property, Paleozoic volcanics occur only as widespread roof pendants within the larger masses of Triassic batholiths.

The development of regional thrust faults placing Carboniferous volcanics on Permian limestone, widely developed tectonic foliations and a variety of mesoscopic fold orientations testifies to the complex structural history of the area. In the western part of the property near Tatsamenie Lake, earlier structures are truncated and offset by younger north-south trending faults, which comprise the Ophir Break. These faults may be traced south to the Golden Bear mine area, where they include the ore-hosting structures of the Golden Bear gold deposit. The Ophir Break is a deep crust-transecting structure, as suggested by the presence of several slices of mantle tectonite (serpentinite) along the main fault strands.

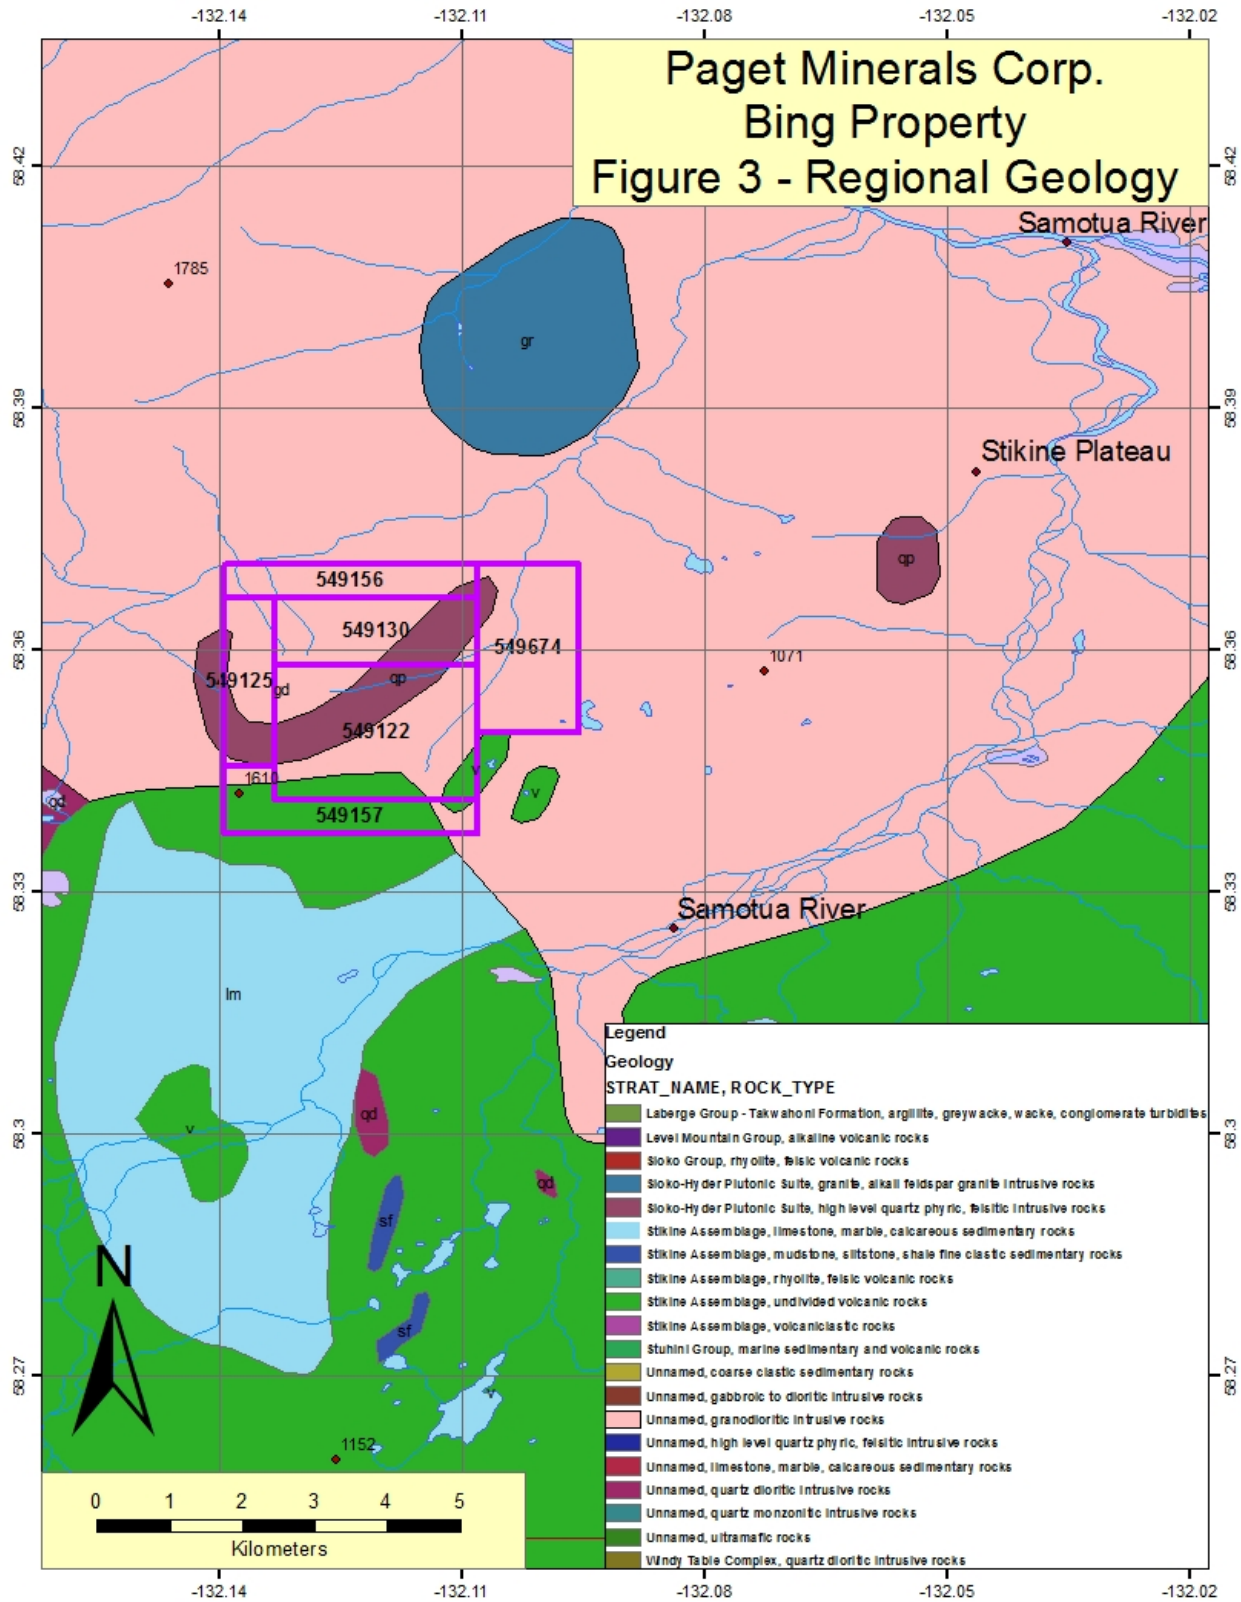


Figure 3: Regional Geology

Property Geology

Bing Area

The Bing area is a flat-topped plateau in the eastern part of the property east of a major north-flowing tributary of the Sheslay River. This part of the property was visited from August 9 through Aug 14, 2007. The principle lithologies include siliciclastic and calcareous sediments, chert, limestone, and andesitic to mafic volcanics (Figure 4). These are intruded by a diorite pluton and a number of intermediate to felsic dykes and stocks (monzonite-quartz monzonite, feldspar-hornblende porphyry, quartz-feldspar porphyry). The intermediate to felsic intrusive lithologies are younger than the weakly foliated diorite which they have intruded. The main body of quartz monzonite appears to be a north trending dyke which has been traced over a strike length of 2.5 kilometers along the upper eastern slope of the plateau. Limestone and calcareous and siliciclastic sedimentary rocks exposed on the north end of the pluton are variably silicified, hornfelsed and skarned. Intercalated volcanic rocks are skarned and strongly epidotized. Intercalated volcanic and sedimentary rocks exposed on the southeastern slope of the plateau have been metamorphosed to amphibolite and calcsilicate.

Mineralization and Alteration

Bing

The Bing showing (MINFILE 104K 035) is a porphyry copper-molybdenum system with peripheral skarn-type copper mineralization. Alteration and mineralization in the Bing area are widespread and complex. Diorite, which underlies much of the property, has undergone polyphase alteration characterized by strong early stage actinolite-magnetite overprinted by K-feldspar-magnetite and quartz veining as well as retrograde chlorite and epidote. This alteration sequence is seen in the upper reaches of Chalco Creek, the southern of the two creeks with good rock exposures draining the eastern slope of the plateau. The zone is here exposed over a width of 75 meters. Similar alteration is exposed in the lower part of Moly Creek, the northern of the two creeks. More evolved felsic dykes (monzonite, quartz feldspar porphyry, quartz monzonite and granodiorite) cross-cut the altered diorite and appear to postdate the main alteration system, as they typically contain unaltered feldspars and mafic minerals. Some remobilization of secondary copper minerals has taken place along dyke contacts. The felsic intrusions are strongly altered in the vicinity of quartz veins where thick (1 to 2 meter) envelopes of quartz-pyrite-sericite/clay are present. A second, weak K-feldspar alteration and veining event is widespread across the property and cross-cuts earlier alteration including the earlier potassic assemblages, and the felsic intrusive bodies.

Three main types of mineralization were identified on the Bing property: (1) Cu ± Mo associated with quartz veins and potassic alteration in diorite (porphyry style); (2) Mo ± Cu associated with quartz, carbonate, kaolinite veins (epithermal style); and (3) Cu in skarn altered volcanics and calcareous sediments intruded by diorite (skarn style).

1. The upper reaches of Chalco Creek and the lower portion of Moly Creek, where potassic alteration is most intense, have significant amounts of chalcopyrite. The chalcopyrite is mainly associated with K-feldspar-magnetite veins and with potassic selvages of quartz veins. Where the alteration is most intense, up to 30% of the rock is k-feldspar and large patches of exposed surfaces are stained with malachite and azurite. These rocks also contain trace disseminated and fracture controlled molybdenite, and up to 5% disseminated and stringer pyrite. This porphyry style mineralization is hosted within diorite, and appears to be truncated by more felsic dykes and/or stocks which intrude both Chalco and Moly creeks. While this system is hosted in diorite, it could be related to an underlying intrusive body; a possible candidate is a phyllic altered plagioclase pyritic monzonite which is only exposed in a few outcrops along the lower reaches of Moly Creek.
2. A number of northeast striking and moderate to steeply dipping 5-40 cm wide quartz(-carbonate)-kaolinite-sulphide veins are exposed throughout the length of Moly Creek. These veins crosscut the diorite and quartz monzonite intrusive rocks that are exposed in the creek. These laminated veins are composed primarily of clear to white quartz with wispy layers of kaolinite. Pods of massive to semi-massive sulphide are common in these veins and in places can occupy the entire width. Sulfides are mainly pyrite with a trace copper minerals (Cu staining is common), and 1 mm thick bands of molybdenite; molybdenite is also disseminated throughout the veins and wall rock. In some locations these veins contain up to 3% molybdenite. Fine stockworks of a grey sulfosalt are associated with a few of the veins. In the upper reaches of Moly Creek, a banded quartz vein contains approximately 5% galena and 2% sphalerite; however this was the only occurrence of Pb and Zn sulfides. Alteration envelopes to the veins are up to 2 meters wide and consist mainly of sericite-clay-quartz-pyrite with local quartz flooding. These envelopes consist of highly weathered, fractured and broken rock. When silica flooding has stabilized the rock against weathering prominent outcrops of intense boxwork after pyrite are present. These veins represent a low-pH meteoric water-dominated fluid developed in the waning stages of the porphyry system. Their superposition on typical porphyry style alteration and mineralization suggests that the hydrothermal center underwent rapid uplift and erosion as the magmatic-hydrothermal system evolved.
3. On both the northern and southeastern slopes of the Bing area volcanic and sedimentary country rock adjacent to the diorite are intensely hornfelsed and altered to calcsilicate phases. On the northern slope, calcareous sedimentary rocks have been intruded by a hornblende leucodiorite which has undergone variable actinolite-magnetite to epidote-chlorite-pyrite alteration. Pyrite is

widespread in the diorite and chalcopyrite is locally present in minor amounts. The sedimentary rocks have undergone strong metasomatic alteration with development of fine grained garnet, diopside and epidote over a strike length of over 400 meters and thicknesses in excess of 20 meters. Locally, coarse grained cm-scale euhedral brown garnet crystals are also present. Volcanic rocks adjacent to the skarn have undergone intense metasomatic epidote alteration. Copper mineralization in the skarn is strong and pervasive, with 1-3% chalcocite, chalcopyrite and bornite as disseminated blebs (up to 1 cm diameter), and rarely in veinlets. Copper staining is abundant on fracture surfaces.

Adjacent to the skarn in the northeastern part of the zone, there are a number of outcrops of volcanic rocks which have undergone extensive metasomatic alteration and which are also copper bearing. These volcanic rocks are primarily red siliceous plagioclase pyritic dacites which in places are brecciated (possibly due to metasomatism) with silica cement. Up to 20% pyrite in these rocks has been weathered out on exposed surfaces exposing an orange boxwork. In addition 2-3% of the rock volume consists of chalcopyrite veins that are responsible for heavy malachite staining.

On the southeastern slope east of the prominent quartz monzonite dyke, white calcsilicate intercalated with amphibolite is pervasively fractured with malachite and azurite staining on fracture surfaces. This secondary copper mineralization is related to in situ blebs of chalcocite which are widespread within the calcsilicate.

Work Completed 2011

The Bing Property was examined by Paget Minerals personnel from June 1 to August 1, 2011. The purpose of the visit was to evaluate the economic potential of the claims by a diamond drilling program on previously determined targets. A 1005.8m drill program consisting of three diamond drill holes was completed on the eastern side of the Bing Porphyry.

Diamond Drilling

A three hole, 1005.8 meter diamond drilling program was conducted between June 1 and August 1, 2011 on the Bing Property. Tahltan Drilling Services, a partner of Blackhawk Drilling Ltd out of Smithers, BC, was the drill contractor. A JT-2000 heli-portable drill rig was used and transported onsite with a B2 Astar helicopter. The drill holes began in HQ core and then reduced to NQ when necessary.

The purpose of the drill program was to attempt to intersect mineralized outcrops at depth that had been sampled during a 2007 rock sampling program. The drill holes were also selected to fill in gaps from the 1965 Newmont drill program.

Core logging of diamond drill core was performed by a geologist and recorded onto a logging form in Excel. Core logging is focused on the identification of major lithological units and alteration assemblages as well as mineralized intervals and faults.

Core intervals for sampling were tagged, logged and split. One half of each interval is sampled for assay, while the other half is kept for reference in the core box on site, presently stored at the Sheslay Camp, UTM 337150E, 6461600N, Zone 9. Assay samples were placed in plastic sample bags closed with zip ties. Several samples, depending on weight, were placed in rice bags and security sealed with security tags. Assay samples were flown to the Tsayta Airbase in Dease Lake where they were palletized and shipped with Bandstra Transportation Systems to ALS Minerals in Terrace. At the laboratory, the samples were dried crushed and pulverized using standard rock preparation procedures. The pulps were then analyzed for Au using a 30 gram fire assay with AA finish and for 30 elements by ICP. Quality control at the laboratory is maintained by submitting blanks and standards every 10 samples on average.

Drill core logs and analytical results are in Appendix C. Drill collar locations are plotted on Figure 4.

Drill collar locations and information are as follows:

Table 3: Diamond Drill Hole Locations

Drill Hole	East-UTM83	North-UTM83	Elev (m)	UTM-zone	Azm	Incl	TD (m)
PB-11-01	668190	6471684	1422	8	90	-60	374.3
PB-11-02	668170	6471360	1428	8	90	-60	394.7
PB-11-03	668428	6470839	1333	8	90	-60	236.8

Table 4: Notable Diamond Drill Intercepts

Drill Hole	From (m)	To (m)	Interval (m)	Cu (%)	Mo (%)
PB-11-01	12.8	374.3	361.5	0.0607	0.0340
<i>including</i>	34.8	46.7	11.9	0.1342	0.0488
	130.6	132.7	1.1	0.3390	0.0258
	150.7	154.7	4	0.1755	0.0173
	166.7	174.7	8	0.1263	0.0255
PB-11-02	14.9	394.7	379.8	0.0663	0.0149
<i>including</i>	14.9	88.1	73.2	0.1104	0.0112
	74.1	88.1	14	0.1773	0.0308

PB-11-03	6	236.8	230.8	0.0429	0.0076
<i>including</i>	11.6	25.9	14.3	0.1316	0.0182
	228	234.4	6.4	0.2402	0.0224

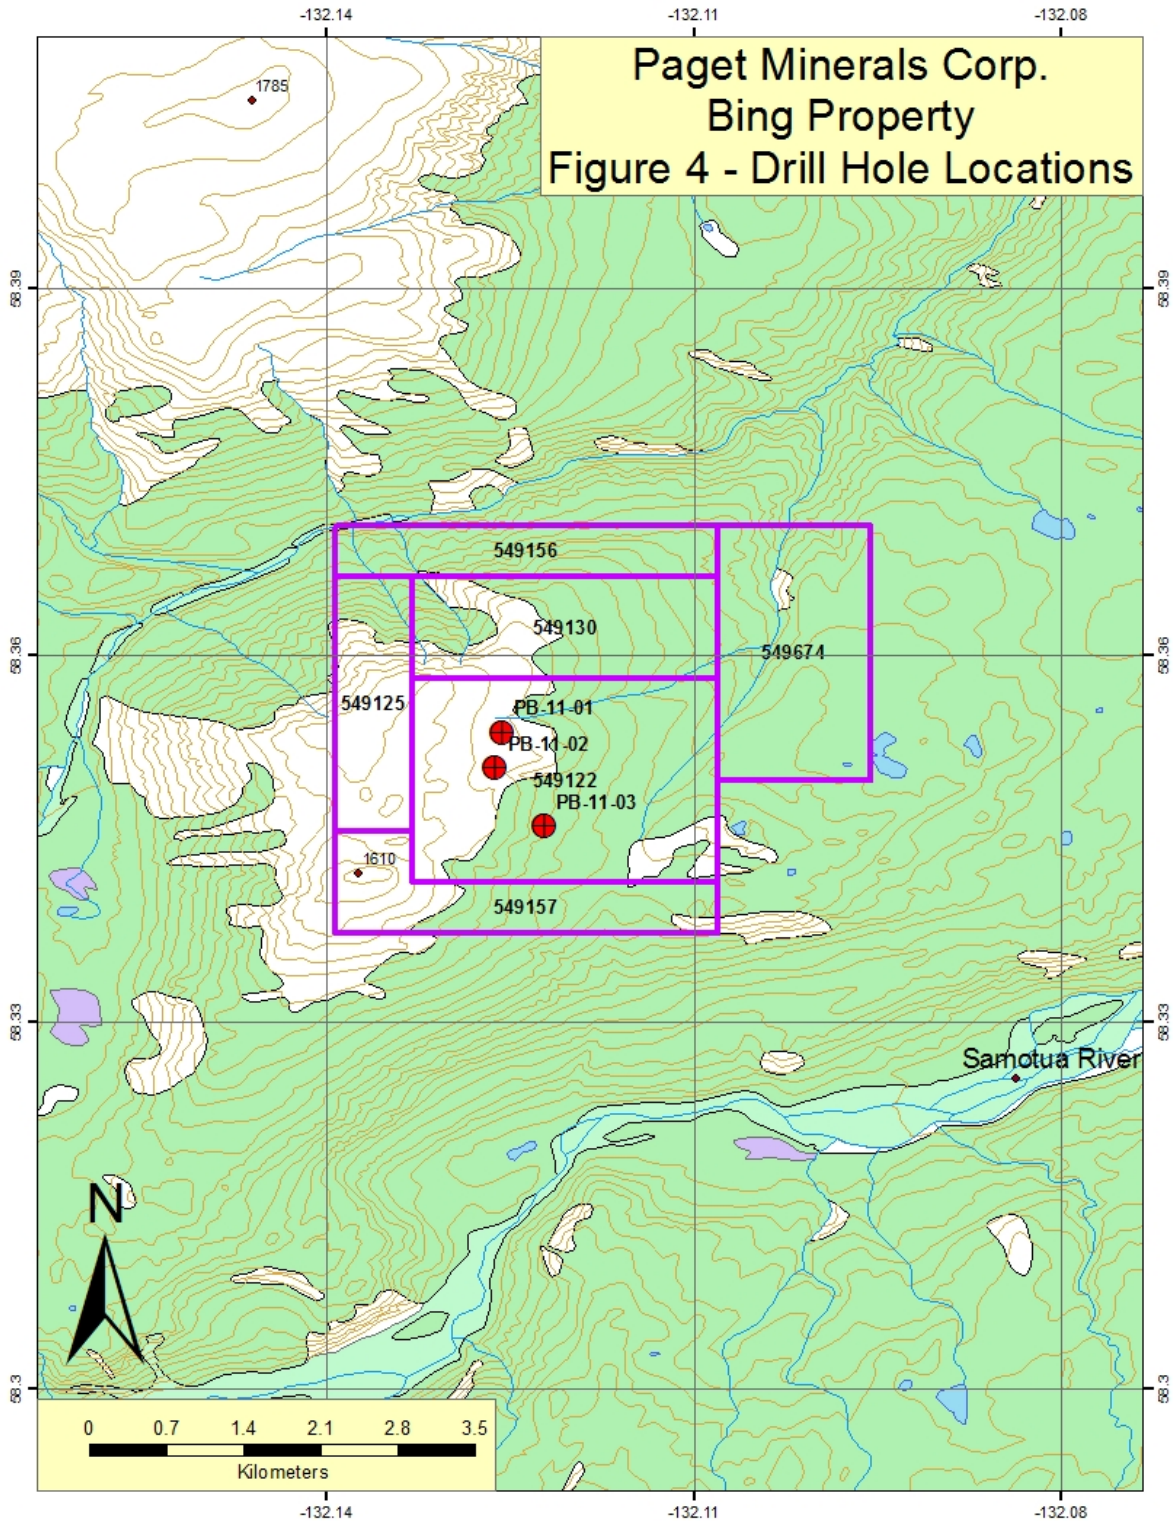


Figure 4: Drill Hole Locations

PB-11-01 – Moly Creek

Diamond drill hole PB-11-01 is located to the south of Moly Creek and drilled due East, following the topography downslope. The purpose of this drill hole was to test for subsurface mineralization based on a rock sampling program in 2007 by Paget that returned values up to 0.2% Cu and 0.26% Mo. Previous drilling had been conducted in this area to the north of Moly Creek in 1965 with some favorable intercepts such as 109 meters at an average 0.24% Cu including 21 meters at 0.86% Cu. These previous drill holes were all drilled with a dip of -45 degrees, at to a maximum depth of 174m. PB-11-01 was drilled with the intent of drilling deeper at a steeper dip to determine the extent at which mineralization occurs at depth.

The hole was comprised almost exclusively of a fine to medium grained diorite except for a few later stage quartz monzonite dykes between 0.9m and 4m wide. The main alteration present throughout the hole was a quartz-chlorite (QC) that resulted in intense silica replacement throughout and 10-20% of the mafics being replaced to chlorite, more in some places. Down hole, epidote alteration began to show up and along with some carbonate veining. The strongest epidote was associated with quartz veins and was commonly associated with minor potassium feldspar alteration. Mineralization tended to decrease downhole. Pyrite is the most abundant sulphide in this hole, occurring as veinlets, fracture coatings, salvages on quartz veins and also finely disseminated throughout. Uphole the pyrite content ranged from 1-3% and decreased downhole to consistent trace amounts. Molybdenite and chalcopyrite typically occur as salvages along the edges of quartz veins, veinlets and fracture coating.

PB-11-02 – Chalco Creek

Diamond drill hole PB-11-02 is located on the north edge of Chalco Creek and drilled due East, following the topography downslope. The purpose of this drill hole was to test subsurface mineralization that is visible in Chalco Creek at to attempt to intersect the main body of quartz monzonite that intrudes the diorite. There had also been no previous drilling in the immediate area of Chalco Creek by Newmont in 1965, so this hole attempted to fill this gap. As with PB-11-01, this hole was drilled at a steeper dip and deeper than the holes in the Newmont drilling program.

The major lithology throughout the hole was an intensely silicified diorite that trended into a quartz diorite at 318 meters. A few monzonite dykes and sills were encountered, but none larger than 0.8m. The main quartz monzonite body was never intersected. Silica, Chlorite and epidote alteration was dominant for the first 180 meters of the hole, after which K-spar, silica and sericite alteration began to take over. Pyrite is the most abundant sulphide in the hole, occurring as veinlets, associated with quartz veins and finely disseminated throughout. Chalcopyrite is fairly consistent throughout the hole in trace amounts, usually associated with pyrite, but sometime in 1-3cm blebs by itself. Moly is found in trace amounts throughout the hole, typically associated with the chalcopyrite, and in some thin veinlets and coating fractures.

PB-11-03 – South Zone

Diamond drill hole PB-11-03 is located approximately 0.5 km south of Calcho Creek and about 100 meters lower in elevation than the first two drill holes. This location was selected based on previous drilling in the area that contained anomalous Cu values, rock samples in 2007 and mineralized outcrop in the area that was observed in the 2011 season. The previous holes in the area were drilled in 1965 by Newmont to a maximum depth of 174 meters at a dip of -45. This hole attempted to drill deeper at a steeper dip of -60 and reached a total depth of 236.8 meters.

As with the first two drill holes, the main lithology is an intensely silicified diorite. Quartz monzonite dykes and sills were encountered sporadically from 123 meters to the bottom of the hole. Alteration is fairly consistent throughout the hole with silica being the most intense. Chlorite and epidote alteration is fairly consistent, the mafics in the diorite were altered to chlorite about 20-30% of the time and epidote was commonly associated along the edges of quartz veins and zones in increased K-spar alteration. Mineralization is fairly consistent with pyrite being the dominant sulfide occurring along quartz veins, in thin veinlets and disseminated throughout. Chalcopyrite occurs with quartz veins and as thin stringers in the diorite. Molybdenum is typically found associated with the chalcopyrite and infilling thin fractures. One area of particular note is that the bottom of this hole ended in some of the stronger mineralization of any of the drill holes. Three of the last four samples were anomalous in Cu, Mo and Au and included the only anomalous Au in any of the three drill holes.

Conclusions and Recommendations

Bing

The Bing porphyry may host a number of additional drill targets. However, further geologic mapping and rock sampling should occur prior to drilling, specifically in the heavily treed areas along the eastern and southern ends of the porphyry. Numerous unmapped outcrops likely exist in these areas and 4-6 days of mapping and sampling would help to better define alteration zones and mineralized outcrops. The main quartz monzonite body that intrudes the diorite was not intersected in the drilling, so further mapping of the monzonite would help to locate it in the subsurface.

The high grade of the skarn mineralization in the northern part of the system suggests that this may be a significant target. Limited mapping in this area suggests a potential strike length of at least 500 meters; whether or not this is continuously mineralized is not known. Observed thicknesses of mineralized skarn in outcrop are up to 20 meters. In the southeastern part of the system similar mineralization hosted by fractured intercalated calcsilicate and amphibolite is dominated by secondary copper minerals and should be examined in detail for its leachable copper potential. During the 2011 season, these skarn targets were not located in the field and it is recommended to reassess the mineralization potential for future drilling.

A well-constructed grid exists on the property from historical exploration and could easily be reclaimed for the purpose of sampling and geophysics. The Bing area has well developed soils and a comprehensive soil sampling survey with modern analytical techniques has never been carried out. It may be possible to use ground magnetics to define early stage actinolite-magnetite alteration as well as magnetite-destructive alteration associated with late-stage polymetallic veins and their associated clay-pyrite-silica overprint. The spatial relationship between the diorite hosted copper-molybdenum mineralization and potassic alteration in Chalco Creek and the quartz monzonite associated molybdenum vein mineralization in Moly Creek may be difficult to define without significant drilling.

References

Awram, David I. and Bridge, Dane A. (1997) Report of 1996 Geological, Geochemical, and Geophysical Exploration Work Done on Ant 1-6, Bing 1-5, and Samo 1-4 Mineral

Bradford, J. (2007): Rock Geochemistry and Geological Mapping on the Icy Lake Property. B.C. Ministry of Energy, Mines and Petroleum Resources Assessment Report 29345.

Claims. B.C. Ministry of Energy, Mines and Petroleum Resources Assessment Report 25,150.

Canon, D.M. and Gutrath, G. (1965): Report on Geological Survey Bing No. 15 Claim Group. B.C. Ministry of Energy, Mines and Petroleum Resources Assessment Report 653.

Canon, D.M. and Gutrath, G (1965): Report of Geophysical Surveys, Geological Survey and Geochemical Survey, Bing #48 and Bing # 83 Claim Groups. B.C. Ministry of Energy, Mines and Petroleum Resources Assessment Report 668.

Cukor, V. and Sevensma, P.H (1970): Geochemical Report. B.C. Ministry of Energy, Mines and Petroleum Resources Assessment Report 3,075.

Cukor, V. and Sevensma, P.H (1971): Geological-Geochemical Report. B.C. Ministry of Energy, Mines and Petroleum Resources Assessment Report 3,475.

Dynes, B. (1994): Geochemical Report on the Bind Mineral Claims. B.C. Ministry of Energy, Mines and Petroleum Resources Assessment Report 23,554.

Holtby, M. (1976): Icy Lake Option 104 K/8 E Geological and Soil Geochemistry Report. B.C. Ministry of Energy, Mines and Petroleum Resources Assessment Report 6,019.

Olfert, E.G. (1993): Geological and Geochemical Report on the Chid Property. B.C. Ministry of Energy, Mines and Petroleum Resources Assessment Report 23,431.

Oliver, J. (1991): Geological Evaluation of the Tab Project Tatsa, And Bing Mineral Claims. B.C. Ministry of Energy, Mines and Petroleum Resources Assessment Report 21,987.

Souther J.G. (1971): Geology and Mineral Deposits of the Tulsequah Map-Area, British Columbia; Geological Survey of Canada Memoir 362 and Map1262A.

Appendix A: Statement of Qualifications

STATEMENT OF QUALIFICATIONS

I, David F. Volkert, P.Geo., certify that:

1. I am presently President/CEO of Paget Minerals Corporation with a business address located at:
1210 – 1130 West Pender St.
Vancouver, BC, Canada
V6E 4A4
2. I am a member in good standing of the American Association of Professional Geologists (AAPG)
3. I graduated from the Colorado School of Mines in 1977 with a Bachelor of Science in Geological Engineering.
4. Since 1977 I have been continuously employed in exploration for base and precious metals in North America, South America, Africa and Asia.
5. I supervised and participated in the 2011 exploration program and am therefore personally familiar with the geology of the Bing Property and the work conducted in 2011. I have prepared all sections of this report.

Dated this 8 Day of November, 2011





Signature

David F. Volkert, B. Sc., PGeo


Item	Name	Date	#	Cost	Item total	Sub-total
BING (ICY LAKE) DRILLING WORK COSTS						
Geological - salaries and wages						
			days	daily rate		
	Chris Weldon		36.50	\$416.00	15,322.67	
	Eric Alexander		26.50	\$312.00	8,519.76	
	Kayla Dell		30.50	\$260.00	8,005.00	
	Christian John		23.50	\$260.00	6,185.00	
	Jessica Pitman		8.00	\$208.00	1,664.96	
	Global Geological Services Ltd.		30.00	\$908.50	27,255.00	
	David Volkert		4.00	\$752.11	3,008.45	
	William Young		25.00	\$289.68	7,241.89	
						77202.73
Support personnel						
	0912581 BC Ltd. DBA All day Logistics				75207.00	
	Matrix Aviation Solutions Inc.				39041.30	
	Norad Electric		5.25	600	3150.00	
						117398.30
Camp Rental						
	Matrix Aviation Solutions Inc.		49.00	\$995.00	48755.00	
	Matrix Aviation Solutions Inc.				638.53	
						49393.53
Camp supplies, Camp fuel, first aid equipment, food, expediting						
	D Volkert				48.63	
	Pembrook Mining				21513.60	
	William Young				3116.55	
	Matrix				23310.18	
	ALS Canada				472.50	
	Deakin Industries				1615.16	
	Norad Electrical				1320.14	
	C Weldon				194.41	
	0912581 BC Ltd. DBA All Day Logistics				9298.80	
						60889.97
Communications - satellite phones, radios, satellite data service						
	Matrix				585.52	
	Pembrook				510.60	
	StarLynx Communications				2642.50	
	Tower Communications				2119.50	
	William Young				58.00	
						5916.12
Geochemical						
	Rock sample assays CDN Resource Lab				549.38	
	ALS Canada				20195.70	
	Phils Boxes		555 boxes	\$9 each	4995.00	
	Freight - ALS Canada				1144.76	
						26884.84
Drilling						
	Black Hawk Drilling				207884.38	
						207884.38
MOB/DEMOB COSTS						
Food & Accommodation: travel to/from site						
			man-days	rate		
	Food		14.75	75	1106.25	
	Accomodations		14.75	95	1401.25	
						2507.50
Wages: travel to/from site						
			days	daily rate		
	Salary Geologist C Weldon		1.20	416	500.68	
	Salary Jr Geologist E Alexander		1.25	312	338.84	
	James Ashleman		1.25	750	905.47	
	Project Manager - W Young		11.00	289.68	2900.53	
						4645.52
Vehicle						
	Enterprise Rent a Car				7113.00	
	Matrix Aviation Solutions				2614.14	
	Fuel C Weldon				421.83	
	Fuel W Young				771.79	
						10920.76
						SUBTOTAL drilling/mob-demob 563643.65
Transportation on-site - Helicopter & Fixed Wing						
	Matrix Aviation Solutions				288649.31	
	Pacific Western Helicopter				1039.95	
	Tsayta Aviation Ltd				24116.35	
	Matrix Aviation Solutions - Fuel				62254.49	
						SUBTOTAL helicopter costs: 376060.10
						Allowable helicopter costs (maximum of 50% work) 156902.80
						Assessment work to claim: \$720,546.45

Appendix C: Cross Sections

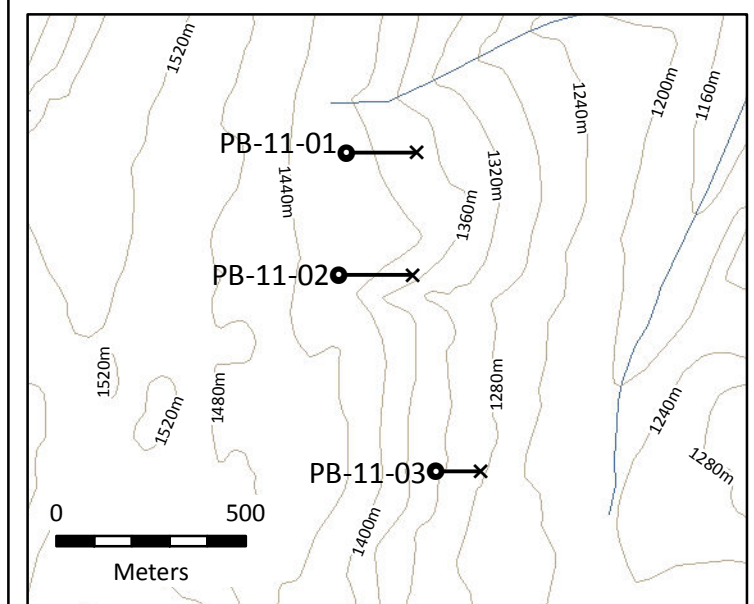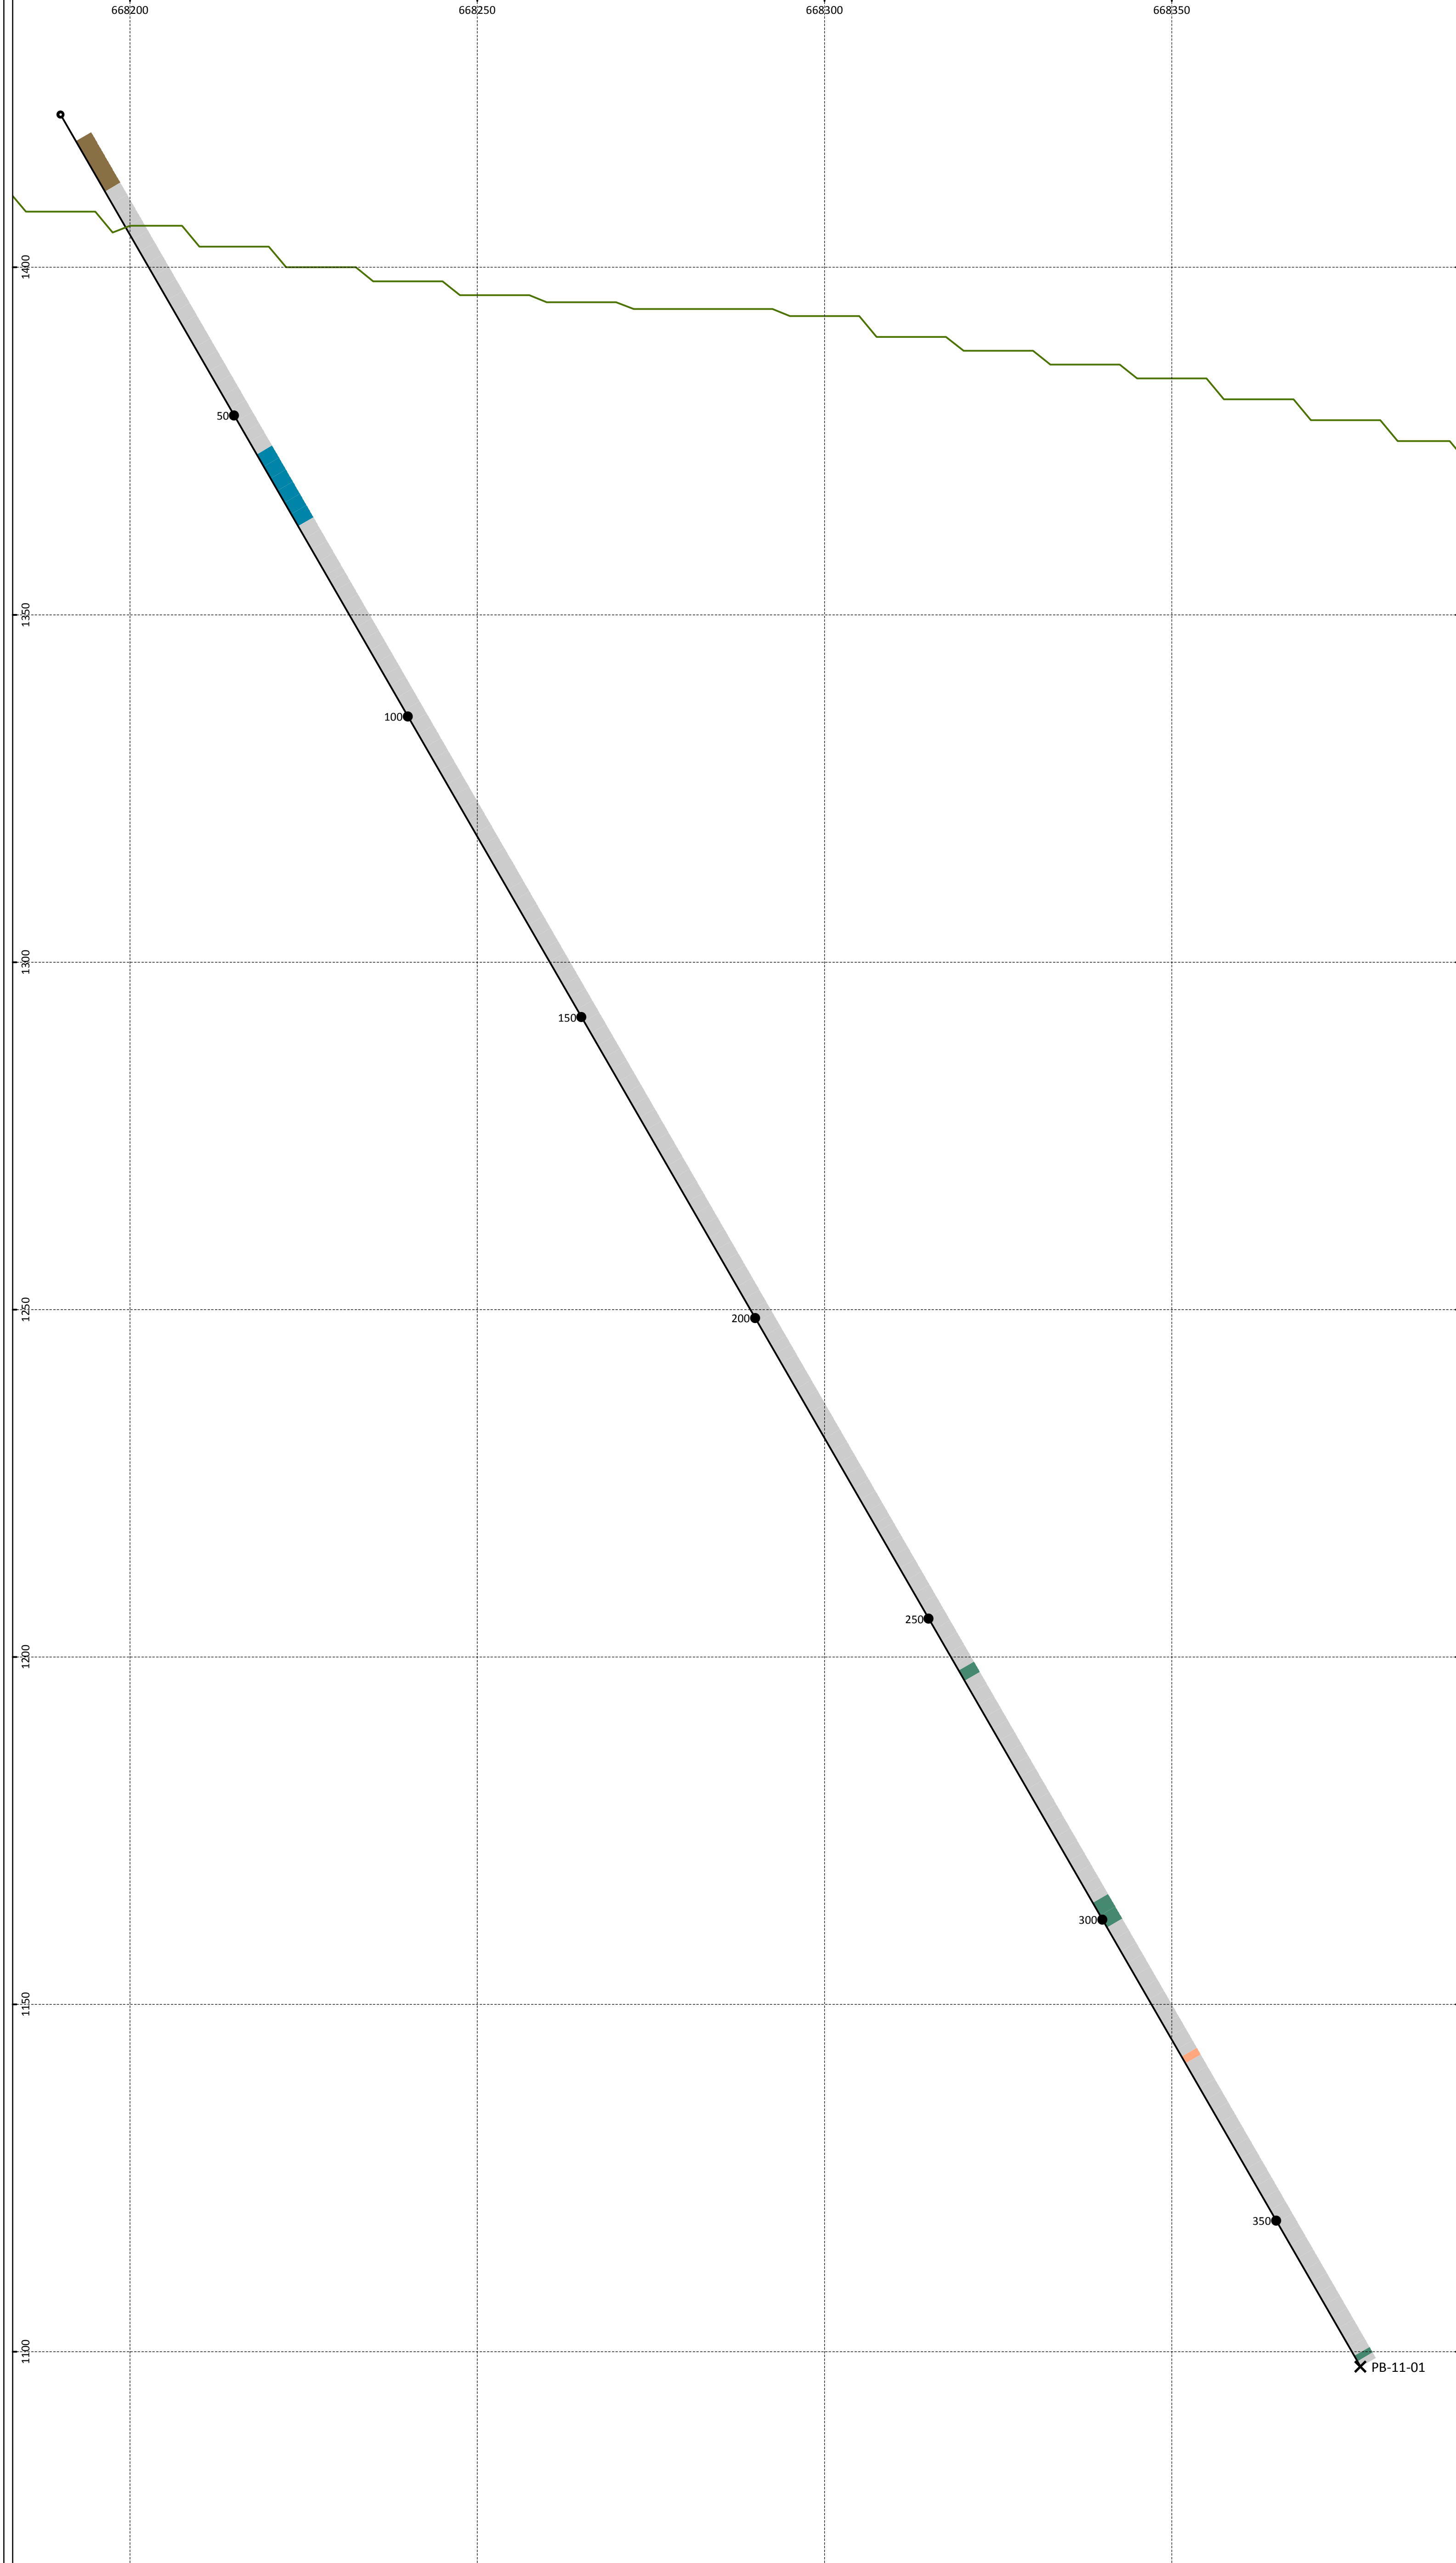


- Drill Collar
 - Topography (DEM NTS 50k)
 - Drill Trace
 - ✕ End of Hole
 - Downhole Depths
- Lithology**
- Overburden
 - Quartz Diorite
 - Felsic Dyke
 - Feldspar Porphyry
 - Silicified Quartz Diorite
 - Fault Zone



Section Details:
 Orientation: East-West
 Viewing: North
 Thickness: 50m +/-



BING PROPERTY
 British Columbia, Canada
Drill Cross Section 6471700N
Downhole Lithology

Date: July 2012 Scale 1 : 500 Coordinates: NAD83 UTM Zone 08



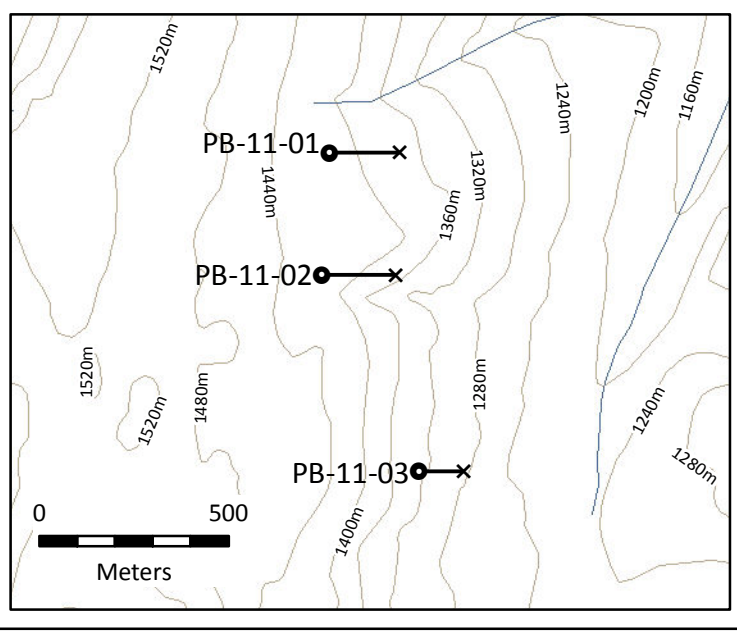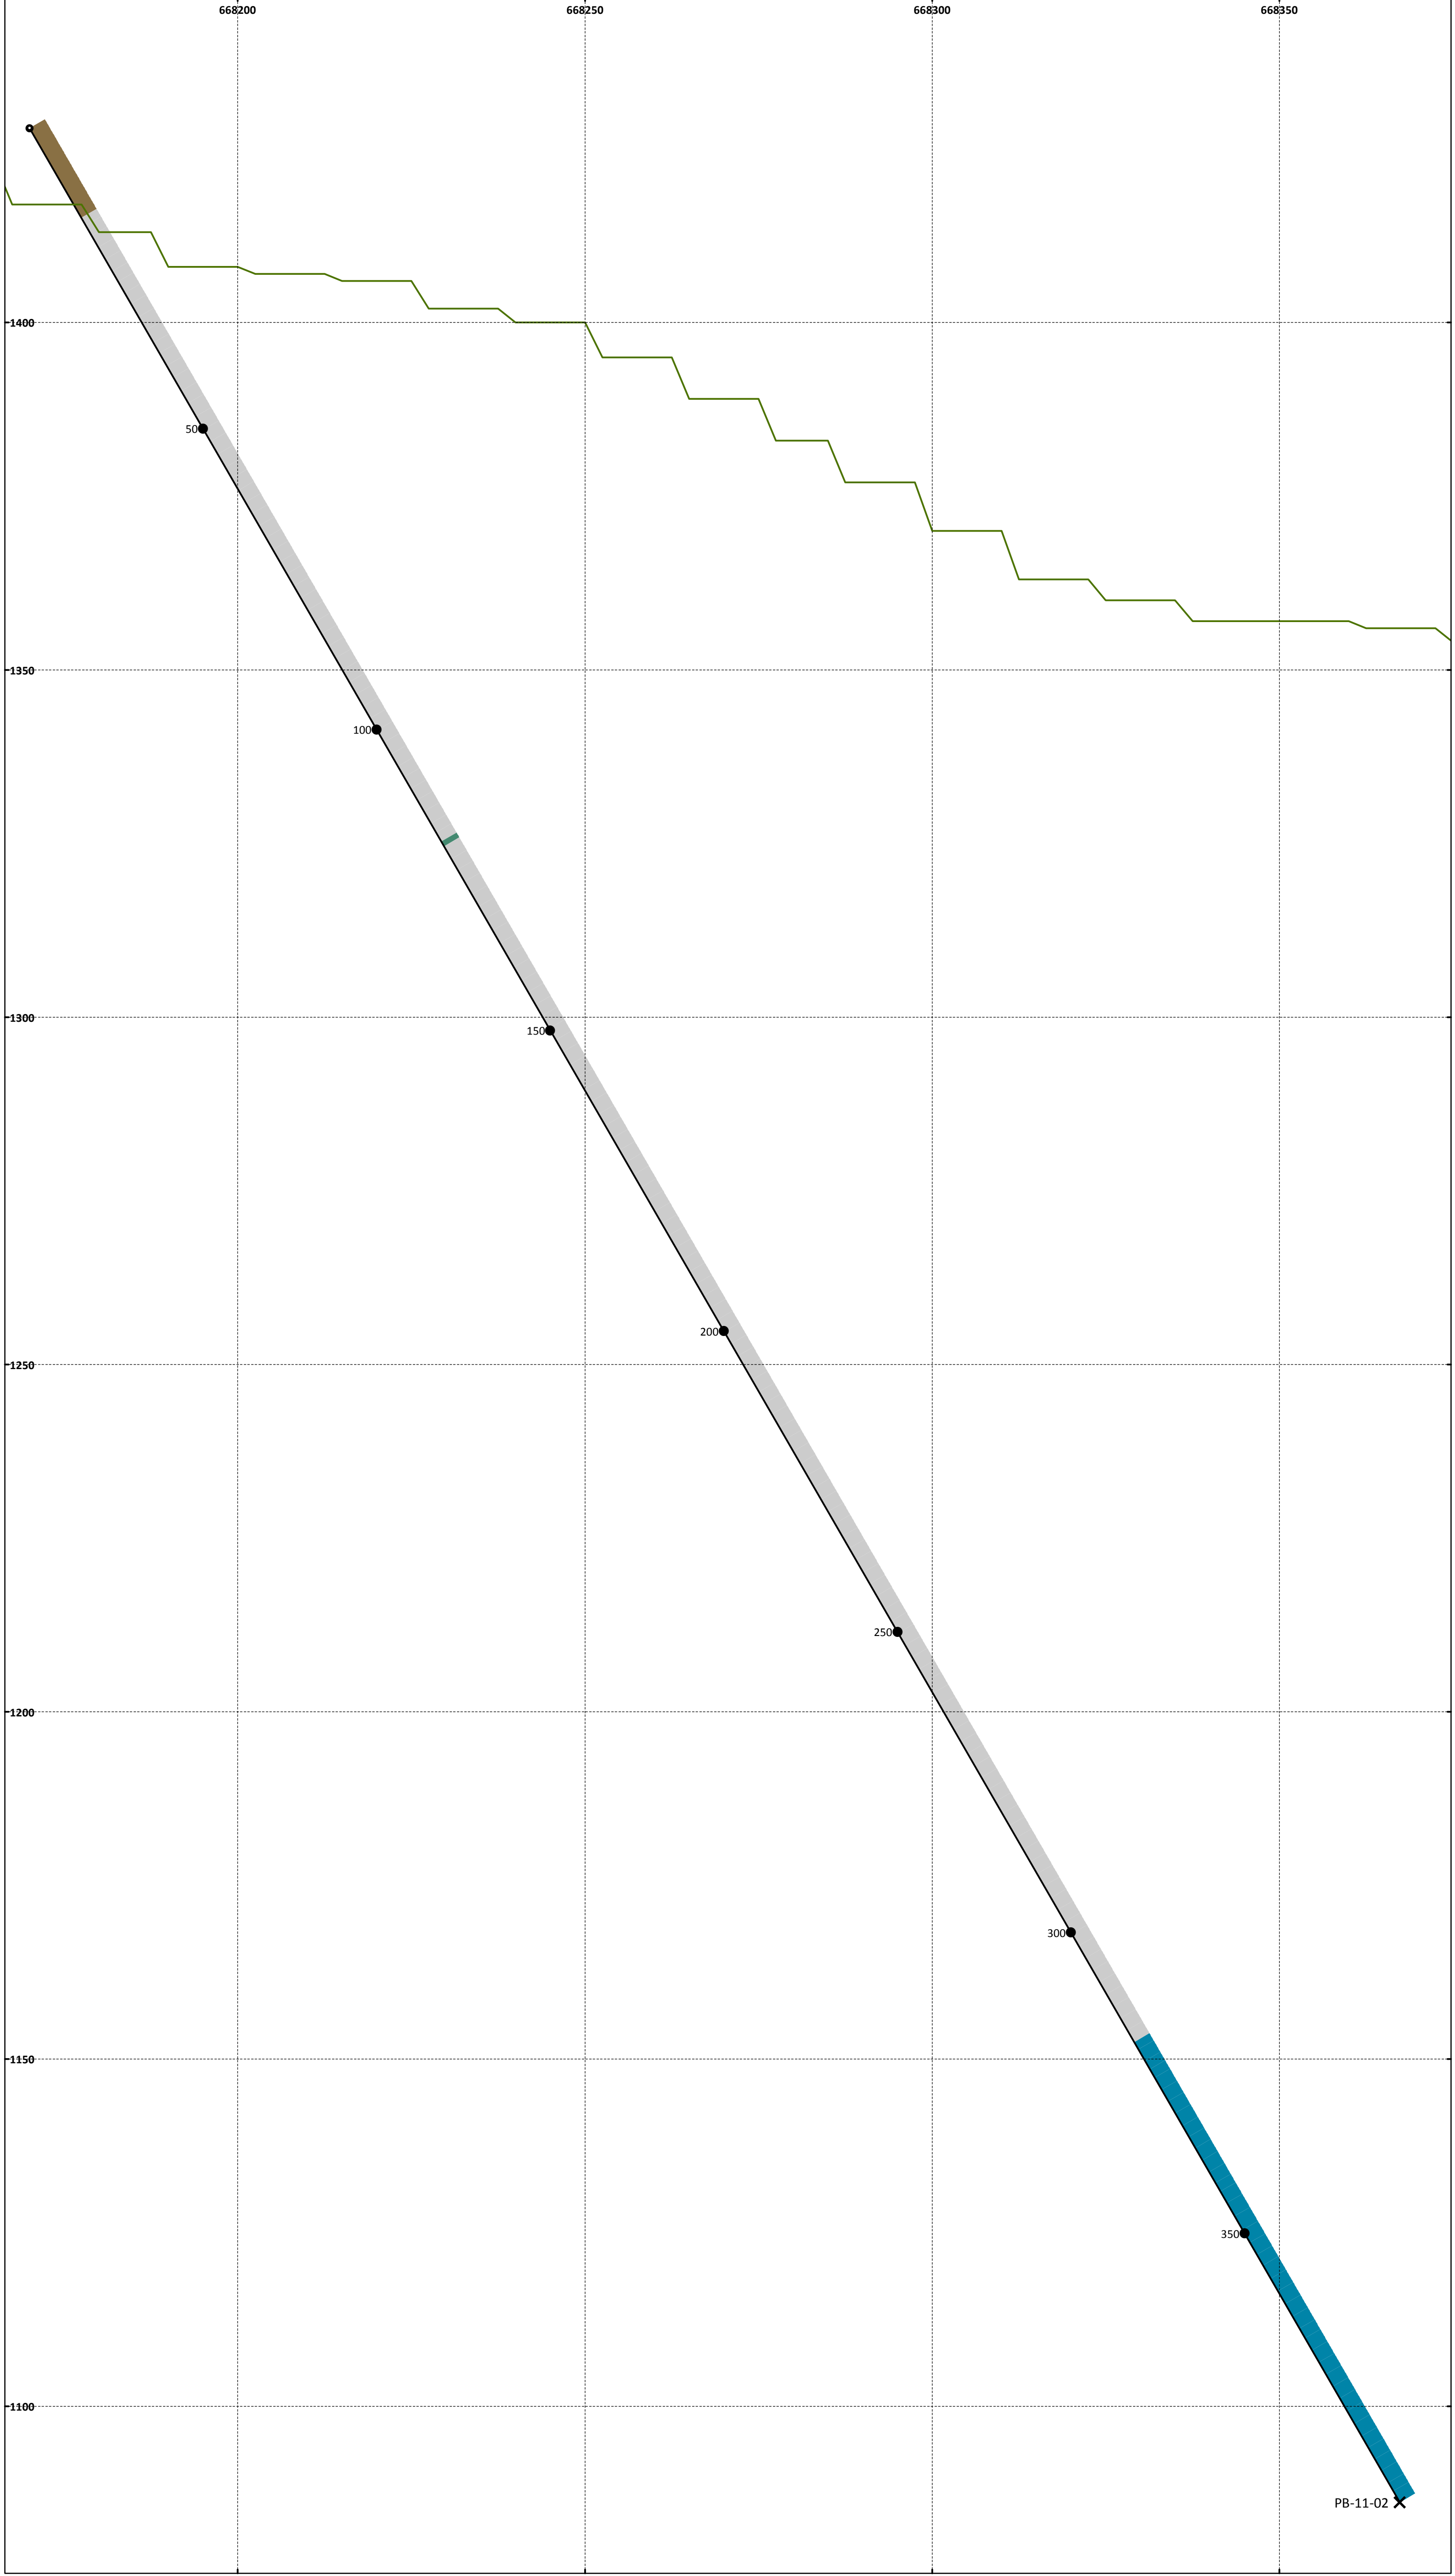


Legend

- Topography (NTS 50k DEM)
- Drill Collar
- Drill Trace
- Downhole Depth
- ✕ End of Hole

Lithology


- Overburden
- Quartz Diorite
- Felsic Dyke
- Feldspar Porphyry
- Silicified Quartz Diorite
- Fault Zone



Section Details:
Orientation: East-West
Viewing: North
Thickness: 50m +/-



BING PROPERTY
British Columbia, Canada
Drill Cross Section 6471300N
Downhole Lithology


Date: July 2012 Scale 1 : 500 Coordinates: NAD83 UTM Zone 08



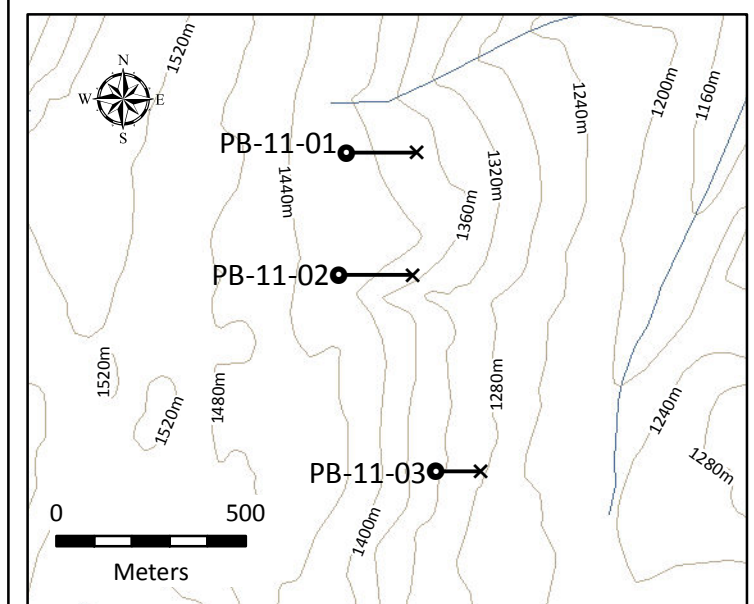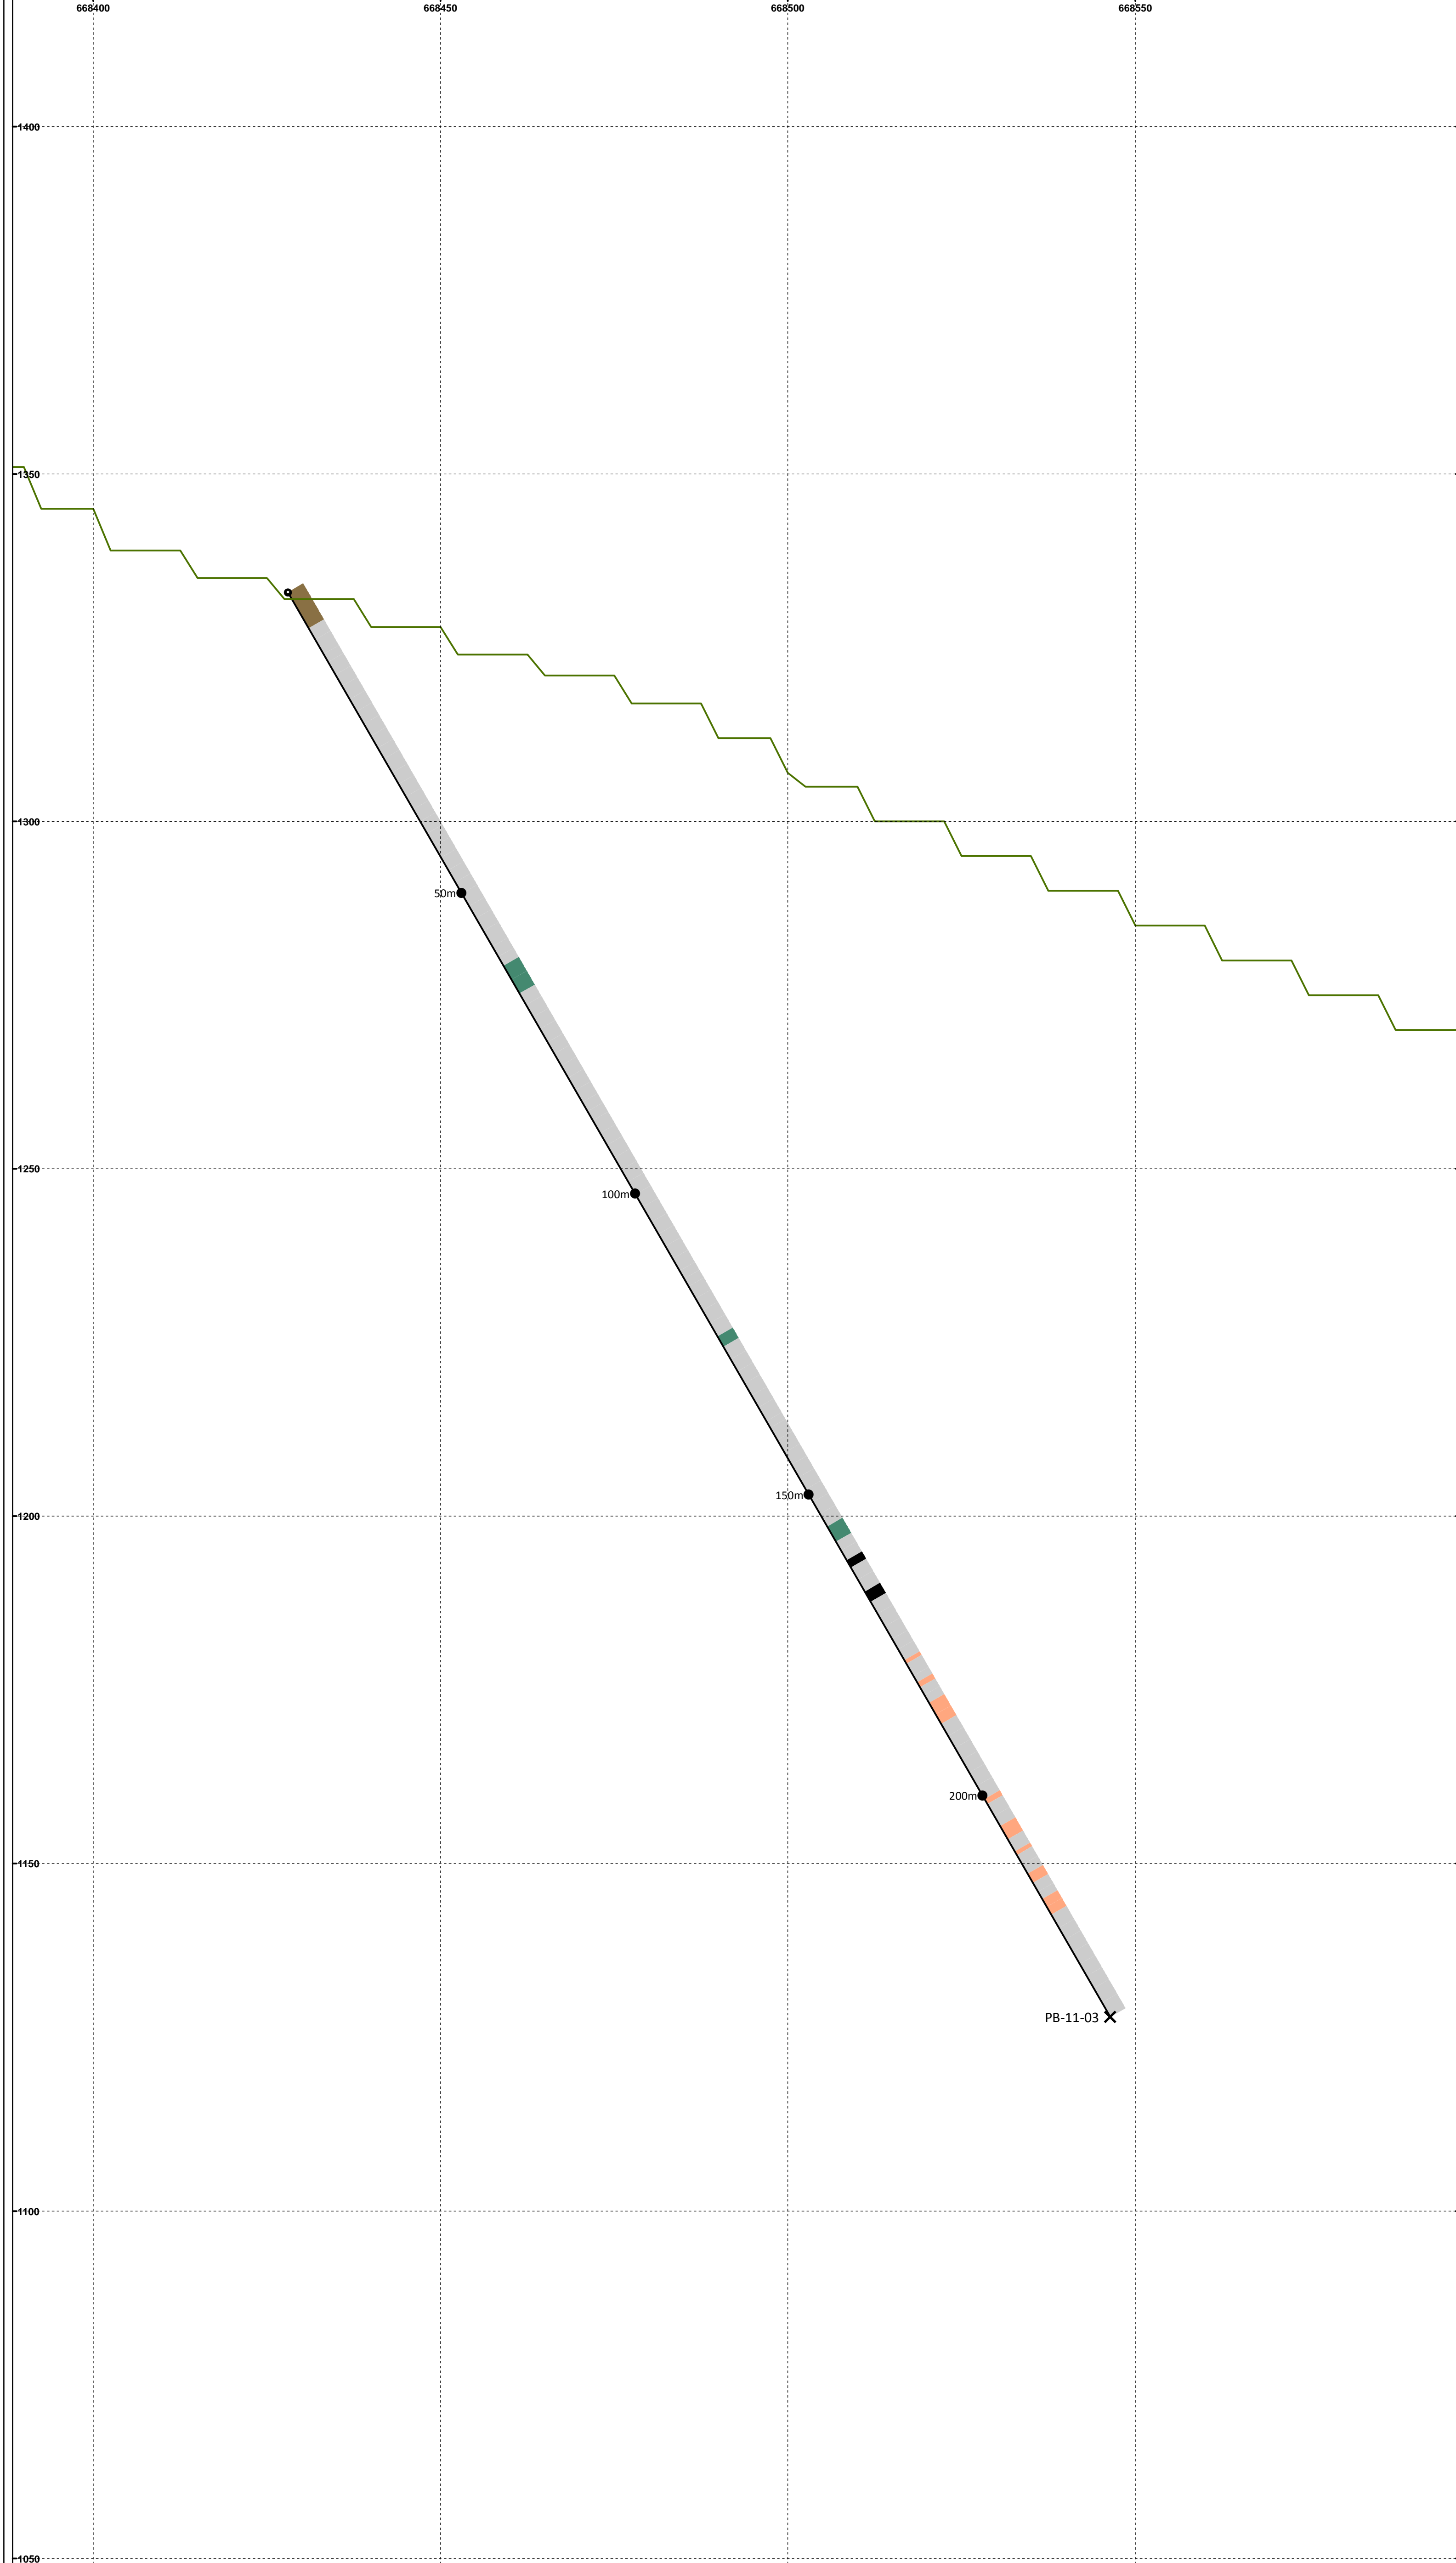


- Topography (NTS 50k DEM)
 - Drill Collar
 - Drill Trace
 - Downhole Depth
 - ✕ End of Hole
- | Lithology | |
|--|-------------------|
| | Overburden |
| | Quartz Diorite |
| | Felsic Dyke |
| | Feldspar Porphyry |
| | Fault Zone |

Section Details:
 Orientation: East-West
 Viewing: North
 Thickness: 50m +/-





BING PROPERTY
 British Columbia, Canada
Drill Cross Section 6470900N
Downhole Lithology


Date: July 2012 Scale 1 : 500 Coordinates: NAD83 UTM Zone 08



Meters

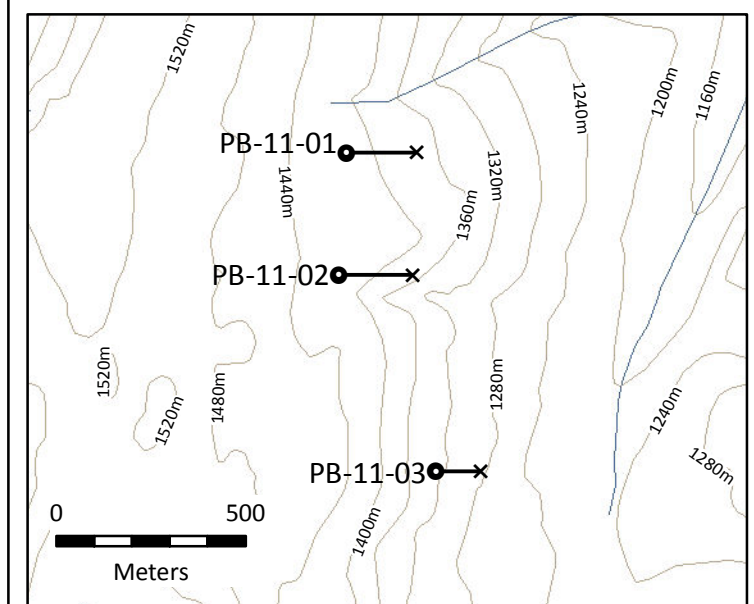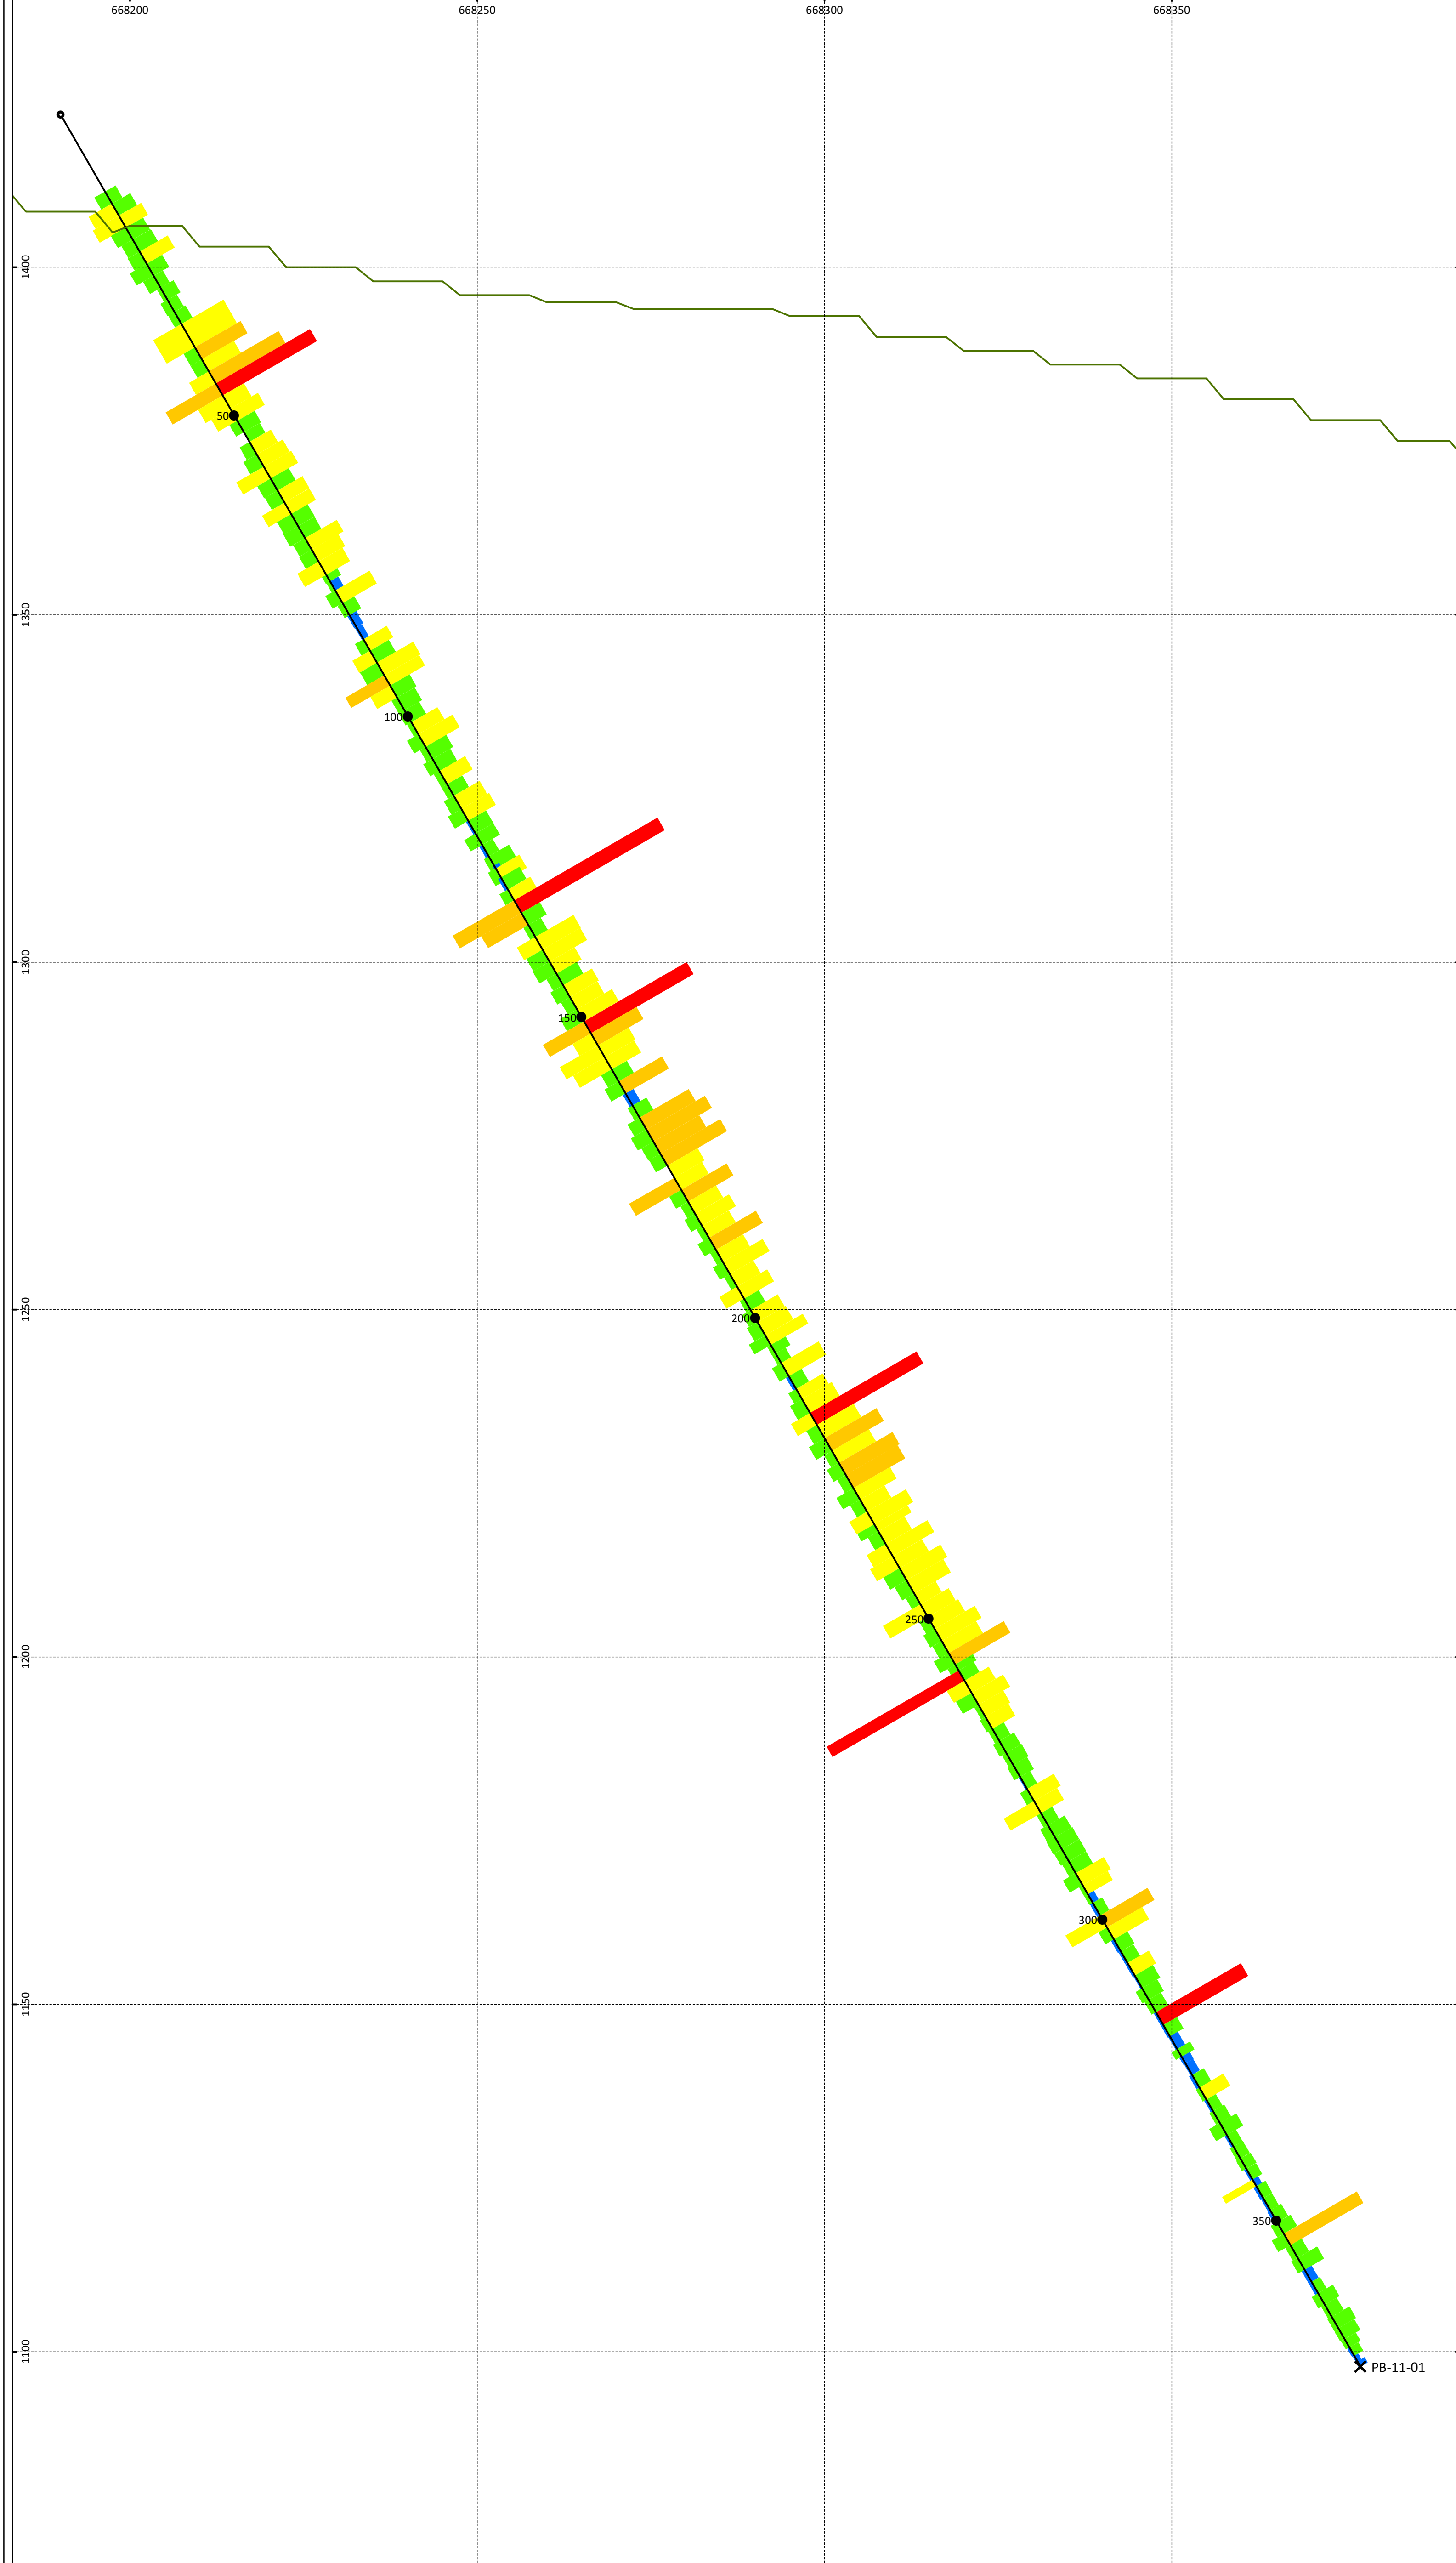




<ul style="list-style-type: none"> Topography (NTS 50k DEM) Drill Collar Drill Trace Downhole Depth End of Hole <p>Section Details: Orientation: East-West Viewing: North Thickness: 50m +/-</p>	<p>Downhole Gold Assays</p> <p>Au (ppm) Left Side</p> <ul style="list-style-type: none"> 0.11 - 0.20 0.06 - 0.10 0.04 - 0.05 0.01 - 0.03 0.00 	<p>Downhole Copper Assays</p> <p>Cu (ppm) Right Side</p> <ul style="list-style-type: none"> 2000.01 - 4000.00 1000.01 - 2000.00 500.01 - 1000.00 200.01 - 500.00 38.00 - 200.00
--	---	---




BING PROPERTY
British Columbia, Canada
Drill Cross Section 6471700N
Downhole Assays

Date: July 2012 Scale 1 : 500 Coordinates: NAD83 UTM Zone 08



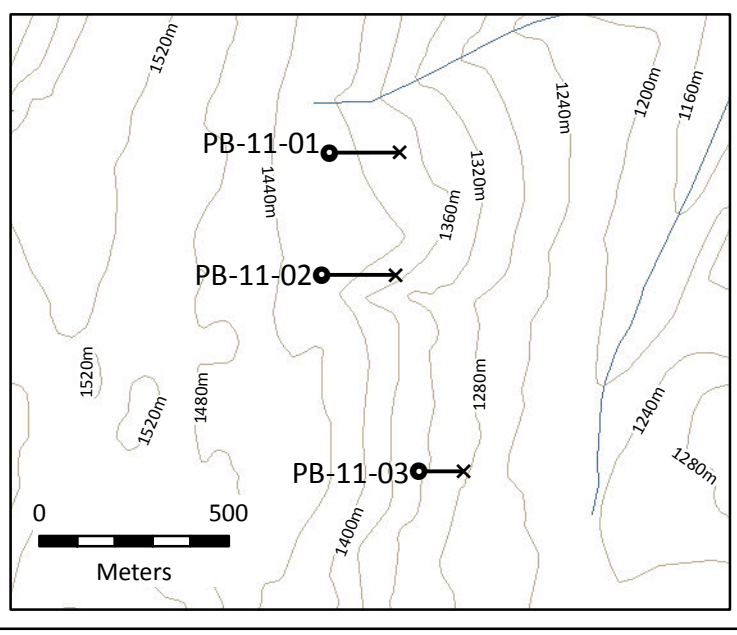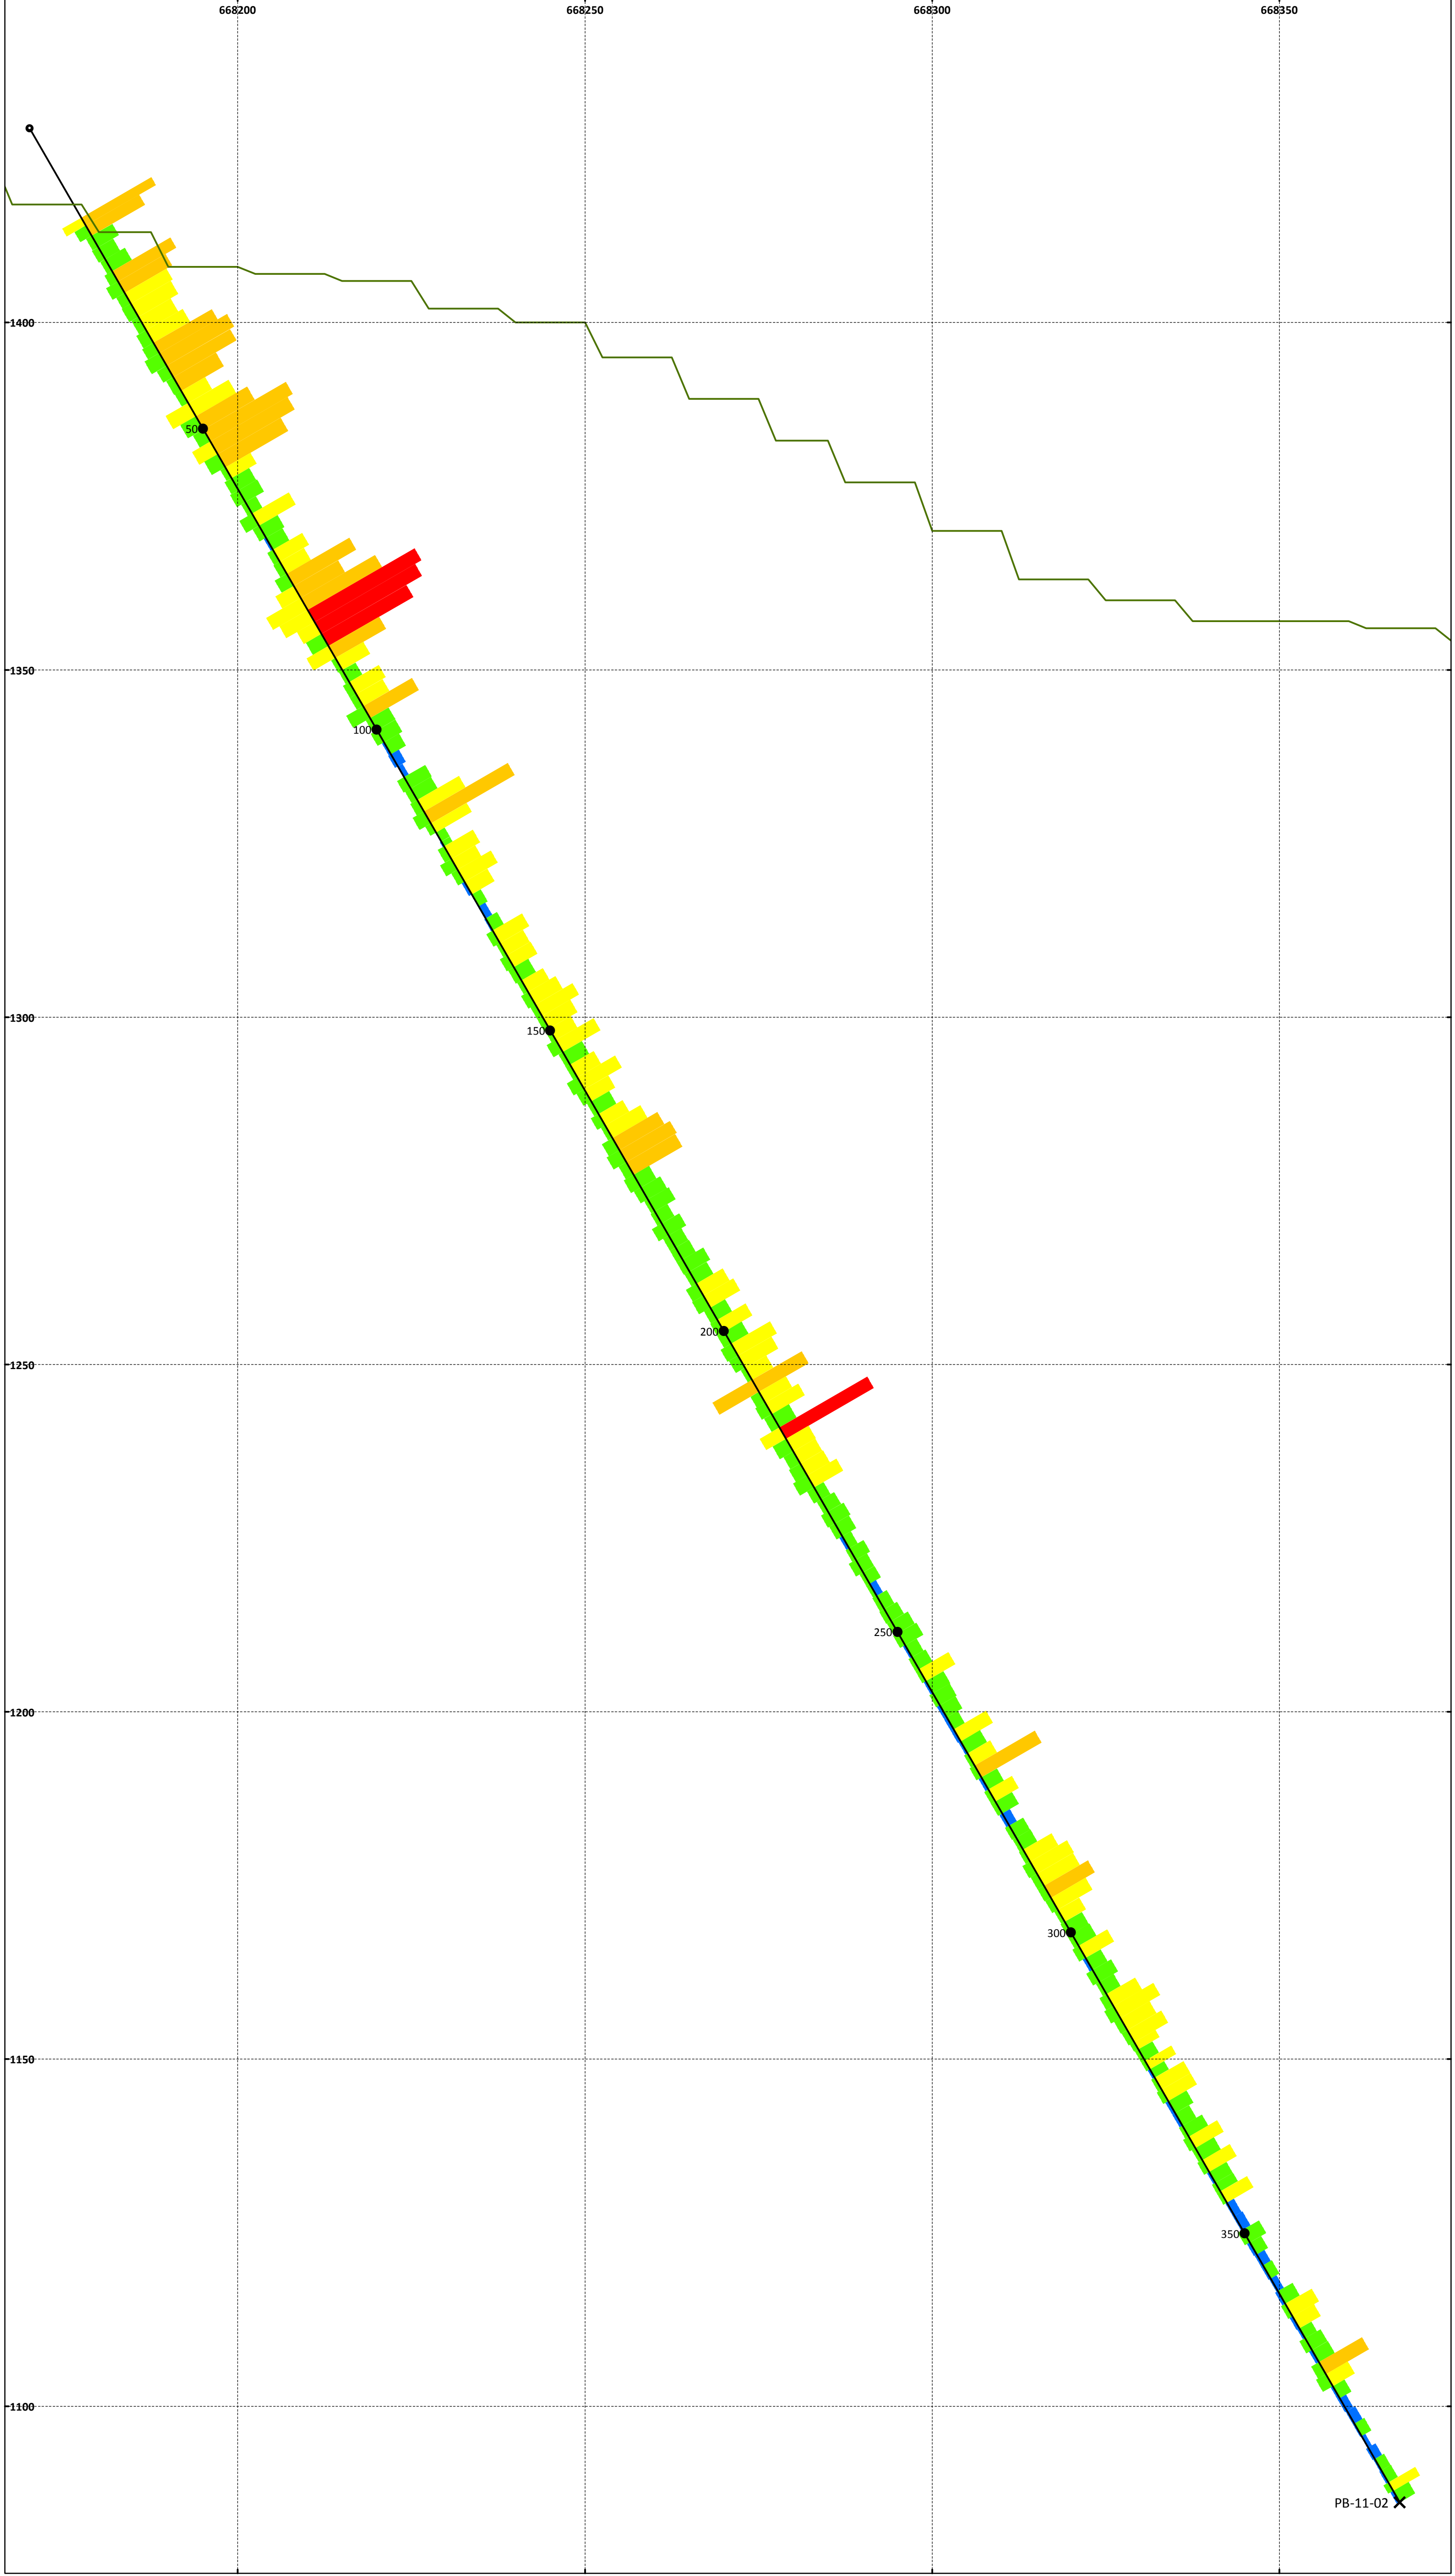




<ul style="list-style-type: none"> Topography (NTS 50k DEM) Drill Collar Drill Trace Downhole Depth End of Hole <p>Section Details: Orientation: East-West Viewing: North Thickness: 50m +/-</p>	<p>Downhole Gold Assays</p> <p>Au (ppm) Left Side</p> <ul style="list-style-type: none"> 0.11 - 0.20 0.06 - 0.10 0.04 - 0.05 0.01 - 0.03 0.00 	<p>Downhole Copper Assays</p> <p>Cu (ppm) Right Side</p> <ul style="list-style-type: none"> 2000 - 4000 1000 - 2000 500 - 1000 200 - 500 38 - 200
--	---	---




BING PROPERTY
British Columbia, Canada
Drill Cross Section 6471300N
Downhole Assays

Date: July 2012 Scale 1 : 500 Coordinates: NAD83 UTM Zone 08



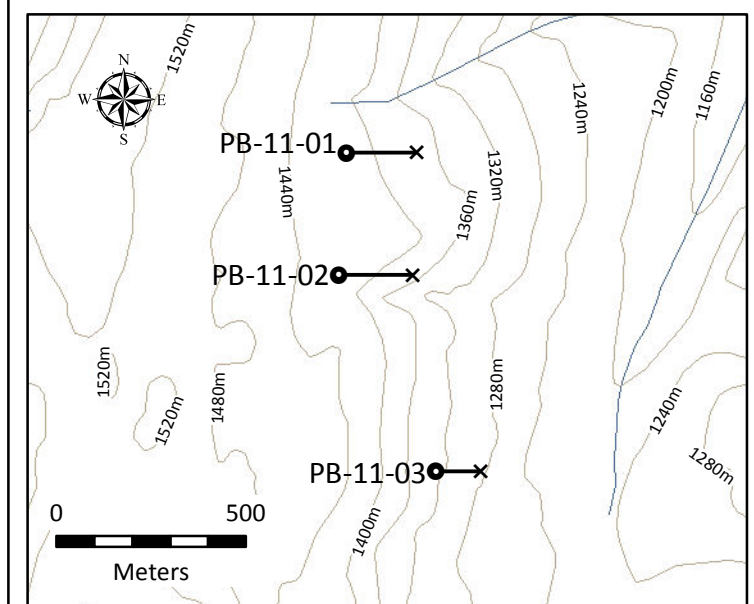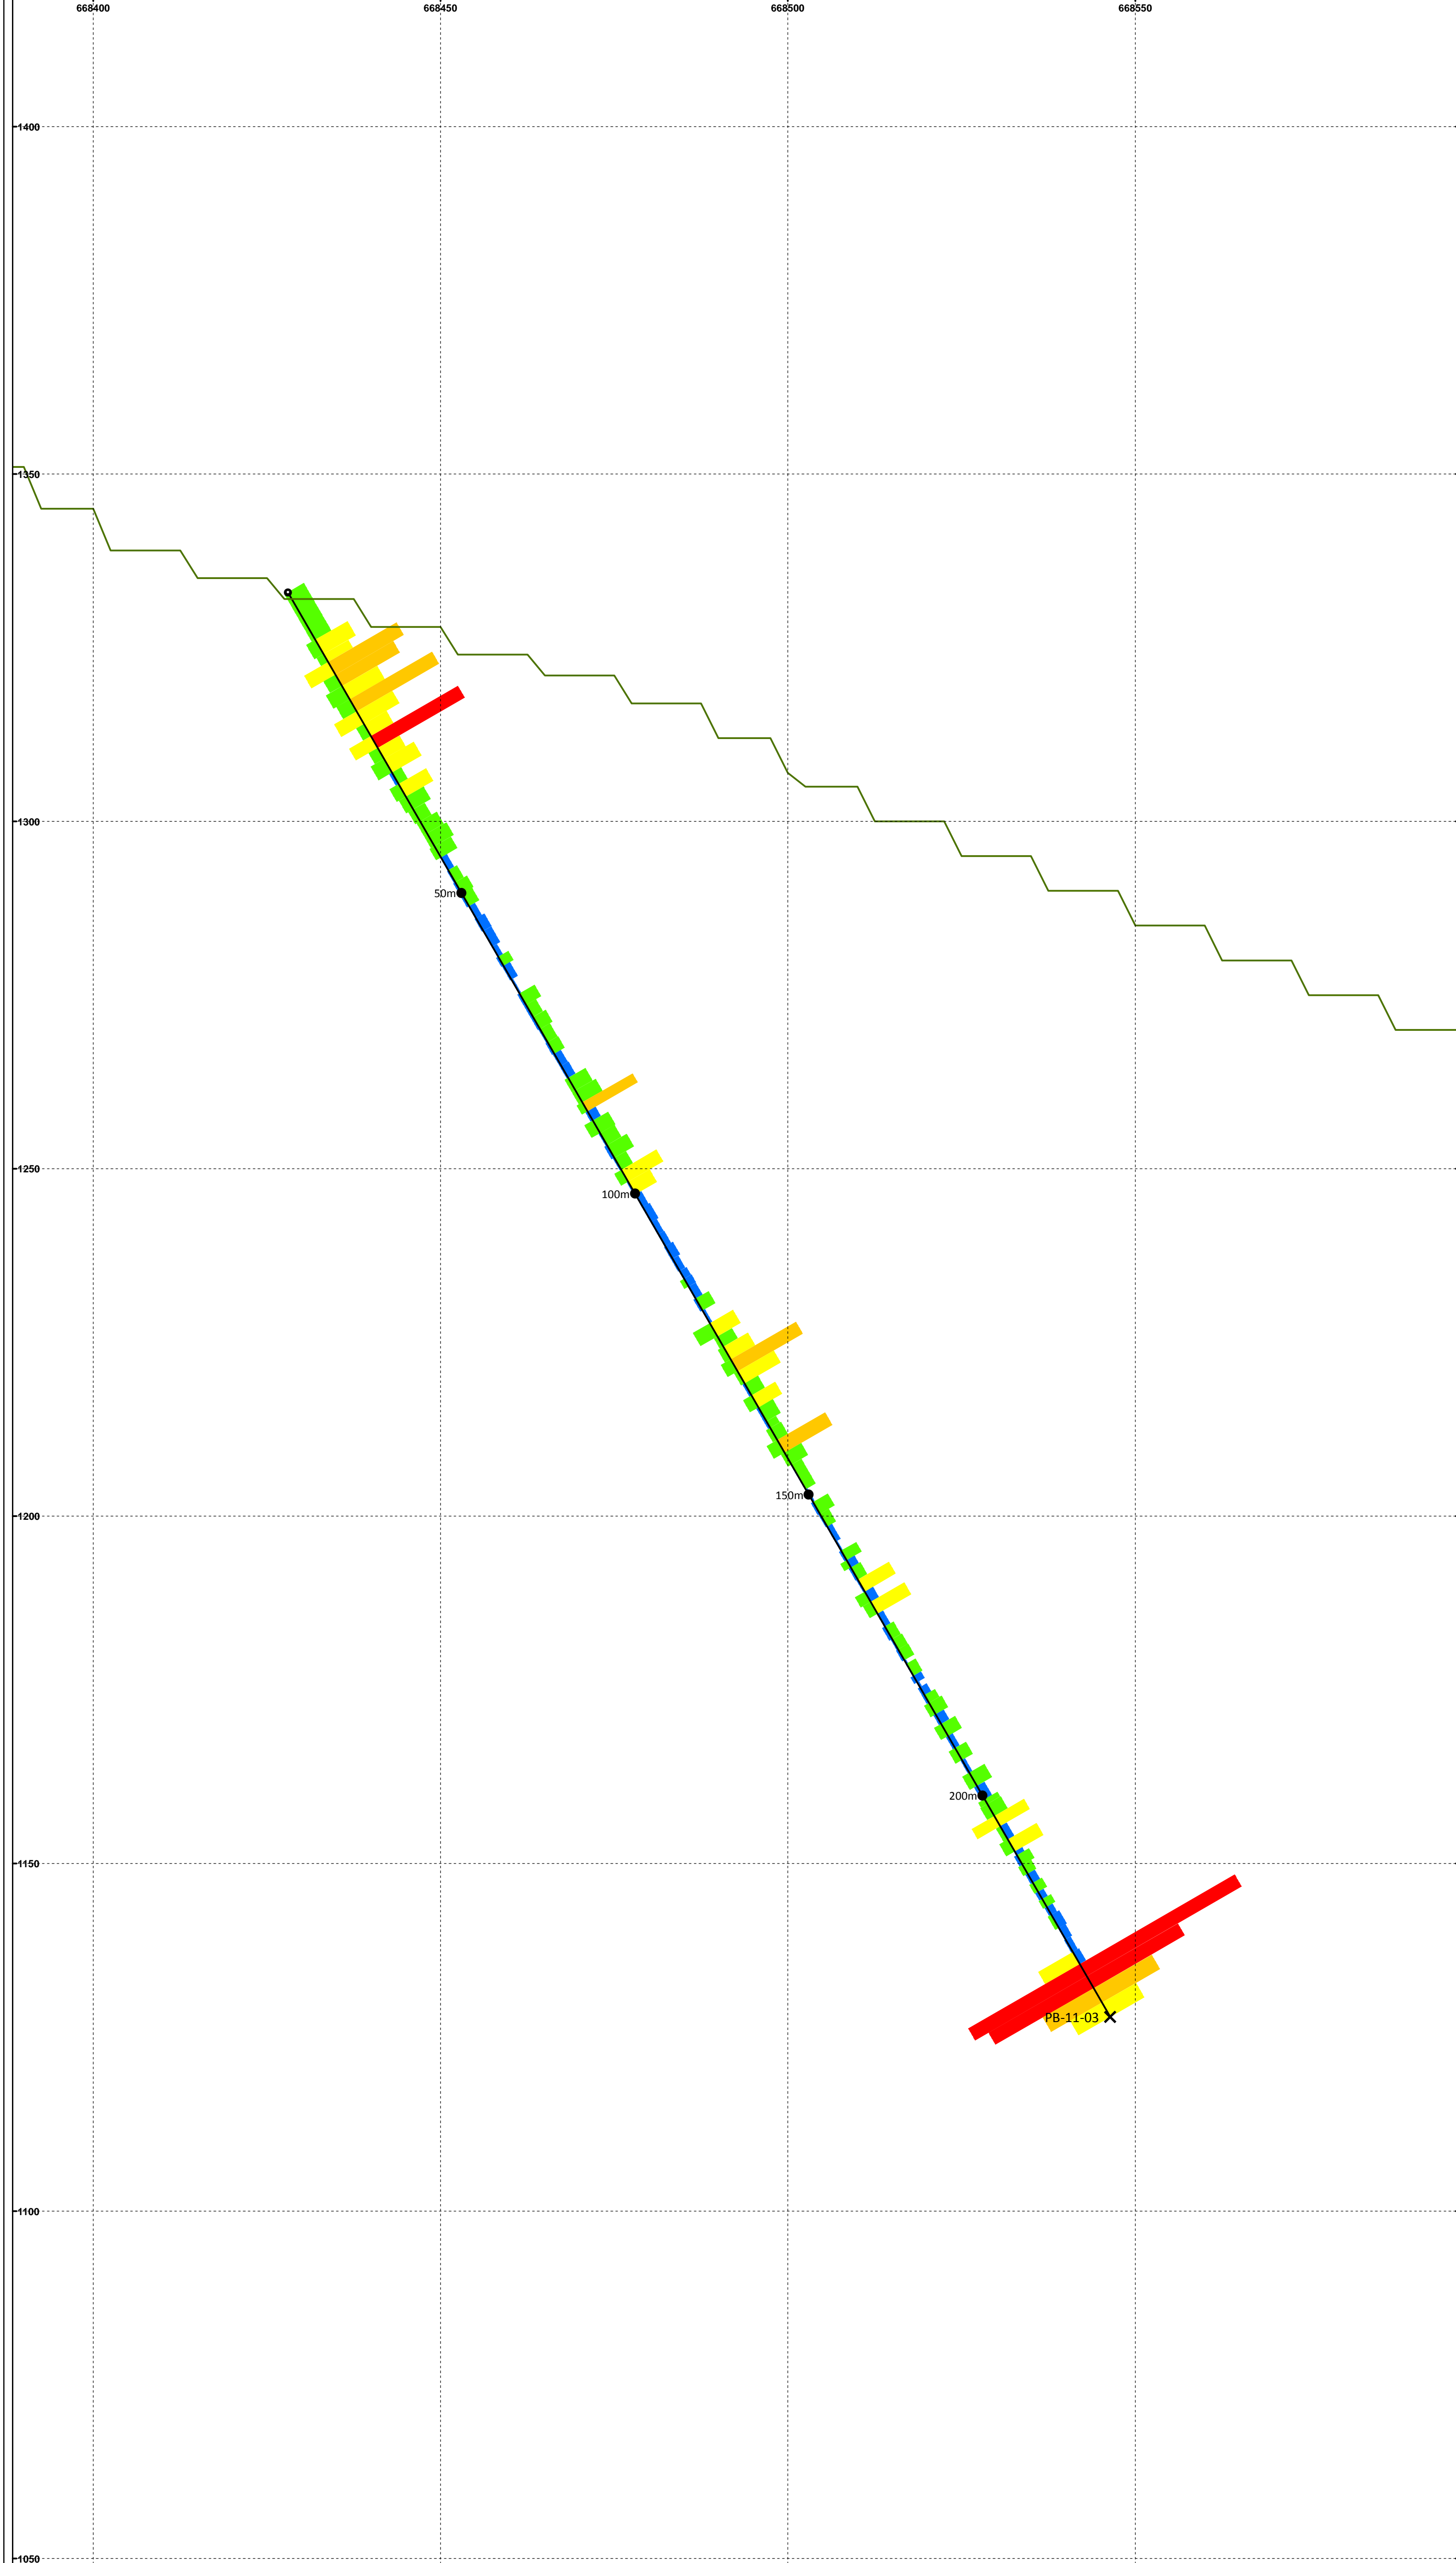


<ul style="list-style-type: none"> Topography (NTS 50k DEM) Drill Collar Drill Trace Downhole Depth End of Hole <p>Section Details: Orientation: East-West Viewing: North Thickness: 50m +/-</p>	<p>Downhole Gold Assays</p> <p>Au (ppm) Left Side</p> <ul style="list-style-type: none"> 0.11 - 0.20 0.06 - 0.10 0.04 - 0.05 0.01 - 0.03 0.00 	<p>Downhole Copper Assays</p> <p>Cu (ppm) Right Side</p> <ul style="list-style-type: none"> 2000.01 - 4000.00 1000.01 - 2000.00 500.01 - 1000.00 200.01 - 500.00 38.00 - 200.00
--	---	---



BING PROPERTY
British Columbia, Canada
Drill Cross Section 6470900N
Downhole Assays

Date: July 2012 Scale 1 : 500 Coordinates: NAD83 UTM Zone 08



Appendix D: Core Logs

BC-11-01

PROJECT: BING
 ID Hole: PB-11-01
 Core Inclination: -60
 Azimuth: 90
 Length: 374.3 m

Start Date: 29-Jun-11
 End Date: 17-Jul-11
 Size: HQ 0- NQ

Drill Contractor: Black Hawk

Collar: UTM (NAD83)
 UTM_E: 668190
 UTM_N: 6471684
 UTM_Zone: 8
 Elev: 1422 m

Geologist:
 Date Log completed: Pg of

Paget Minerals Corp.

Sample Number	From	To	Length	Geology - Lithology			Lithology	Rock type/texture	Rock composition	Structure						Veins/1m						Alteration						Mineralization						Description					
				Graph Log	Redox O/M/S	Alter. Code				Rock Code	Type (F, f, B, v)-Angle						Breccia	Sulfide	Qtz-Sulf/Ox	Quartz	Mnt±qtz	Other	biotite	K-fspar	Sericite	Silica	Clays	Chlorite	Epidote	Calcite	Other	Oxide / Limonite	HGJ Ratio		Magnetite %	Other: Cu, Mn, etc.	Pyrite	Cpy	Bornite
	(m)	(m)	(m)						1	<	2	<	3	<																									Ore__py, cpy, bor, cv, sph, gal; Structure__ Bx, F, f, V, v, B; Other__stk, dsm, prvs, mtx, slvg.
	4.4	12.8	8.4				OB																														Overburden		
L480523	12.8	14.8	2		M	QC	Di	Silicified Diorite	fdsp, mafics	v		40																										Silicified Diorite: medium grained to fine grained in highly altered sections, dark grey. Sulphides occur mainly as fracture coatings. Some mixed moly and qtz veins mainly oriented at 40 deg. Oxidation on fracture surfaces. Weak K-spar alt. associated with qtz veining. radial actinolite crystals. Very Silicified.	
L480524	14.8	16.8	2		S	QC	Di	Silicified Diorite	fdsp, mafics	v		50	v	55																								Lithology continues. Increase in chlorite alt. Stronger magnetite, filling fractures. Sulphides mainly occur as Moly mixed with qtz veins dipping from 45-55 deg and pyrite in fracture surfaces.	
L480525	Blank	CDN-BL-8																																					
L480526	16.8	18.8	2		S	QC	Di	Silicified Diorite	fdsp, mafics	v		75	v	20																								Lithology continues. Slight decrease in chlorite alt. Strong py and some moly associated with fractures along qtz veins with k-spar salvages. Some calcite alt. present in vein at 75 deg with some visible moly and py. Long vein alt. to chlorite, with visible py and disseminated moly at 20 de.	
L480527	18.8	20.8	2		S	QC	Di	Silicified Diorite	fdsp, mafics	v		80	v	10																								Lithology continues. Magnetite filling fractures. Slight increase in calcite alt. several .5 mm py vnits running through core. Decrease in py on fracture coatings. Sericite alt. on fracture surfaces.	
L480528	20.8	22.8	2		S	QC	Di	Silicified Diorite	fdsp, mafics	v		85	v	35	f	40																					Lithology continues. 4 cm thick magnetite vein at 85 deg. Strong K-sapr alt along edges qtz vein at 35 deg. With strong chlorite, calcite and epidote alt along center of vein (hematite also present). Moly coating on fracture at 40 deg. Some moly / qtz veins steeply dipping (~70 deg).		

L480529	22.8	24.8	2			S	QC	Di	Silicified Diorite	fdsp, mafics	f	20	v	85					2	3	1			2	1	5	1	4	1	1			1		2		tr	Lithology continues. Carbonate coatings along fractures. Hematite staining along fractures. Moly and qtz vein at 80 deg. At end of sample there is a 20 cm section of increased clay and sericite alt.
L480530	24.8	26.8	2			S	QC	Di	Silicified Diorite	fdsp, mafics	f	75	v	50					2	2	1			3	1	5	1	4	1	1			1		2		tr	Lithology continues. Increase in K-spar alt and slight increase in chlorite alt. Moly fracture coating at 75 deg. Qtz/carb veins present, epidote and pyrite associated.
L480531	26.8	28.8	2			S	QC	Di	Silicified Diorite	fdsp, mafics	v	45	v	80					2	4	2			3	1	5	1	4	1	1			1		2		0.25	Lithology continues. Mixed moly and qtz veins range from 45-80 deg. Py and moly fracture coatings. K-spar alt. associated with qtz veining. Thin oyrile vnlts.
L480532	28.8	30.8	2			S	QC	Di	Silicified Diorite	fdsp, mafics	v	50							2	3	2			2	1	5	1	4	1	1			1		2	0.25	0.25	Lithology continues. Begin to pick up cpy on fractures and small blebs in veins. Decrease in K-spar alt. 2 cm thick qtz vein with py and moly salvages along edges.
L480533	30.8	32.8	2			S	QC	Di	Silicified Diorite	fdsp, mafics	v	75							1	2	2			2	1	5	1	4	1	1			1		2	tr	tr	Lithology continues. Py occurs mainly as fracture coatings and some mixed py/ qtz veins. Still some cpy on fracture surfaces but to a lesser degree. Qtz vein with strong moly salvages at 75 deg.
L480534	32.8	34.8	2			S	QC	Di	Silicified Diorite	fdsp, mafics	v	85	v	45					2	3	4			2	1	5	1	3	1	1			1		2		tr	Lithology continues. Decrease in chlorite alt, mainly confined to fractures. Decrease in magnetite. Qtz vein with moly salvages ranging from 45-85 deg. Increase in qtz/ carb veins.
L480535	Standard	CDN-CM-11A																																				
L480536	34.8	38.7	3.9			S	QC	Di	Silicified Diorite	qtz, fdsp, mafics	v	75	v	50	f	10			3	3	2			2	1	5	1	4	1	1			1		2	0.25	0.25	Lithology continues. Small cpy blebs. Moly salvage son qtz veins. Py and moly as fracture coatings. K-spar alt. associated with qtz veining. Magnetite confined to fractures. Clay, sericite and carbonate on fracture surfaces. Trending towards qtz Di.
L480537	38.7	40.7	2			S	QC	Di	Silicified Diorite	qtz, fdsp, mafics	v	55	f	15	f	40			2	3	3			3	1	5	1	4	1	1			1		2	tr	0.25	Lithology continues. Mixed cpy and qtz vein at 55 deg with moly salvages along edges. Increase in K-spar alt. qtz vien offset 1 cm by later qtz/ calcite vein exploiting fault. Hematite staining on fracture surfaces.
L480538	40.7	42.7	2			S	QC	Di	Silicified Diorite	qtz, fdsp, mafics	v	60	f	45					0	2	3			3	1	5	1	4	1	1			1		1	tr	tr	Lithology continues. Decrease in sulphides. Moly salvages on qtz veins and some disseminated py.
L480539	42.7	44.7	2			S	QC	Di	Silicified Diorite	qtz, fdsp, mafics	v	55	f	15	v	30			2	4	3			3	1	5	1	4	1	1			1		1	0.5	0.25	Lithology continues. Moly as fracture coatings an as qtz vein salvages. Cpy as fracture coatings and in thin vnlts. Qtz/calcite vein. Magnetite filling fractures.
L480540	44.7	46.7	2			S	QC	Di	Silicified Diorite	qtz, fdsp, mafics	v	85	v	90					1	2	3			3	1	5	1	4	1	1			1		1	tr	tr	Lithology continues. Steeply dipping qtz veins with moly salvages along edges, range from 1 -2.5 cm thick. Py, cpy and py as fracture coatings. K-spar alt. associated with qtz veins
L480541	46.7	48.9	2.2			S	AR	Di	Silicified Diorite	fdsp, mafics	v	35	v	60					4	0	0			0	2	5	2	4	0	1			1		3	tr	tr	Lithology continues. Finer grained, more altered Di, less visible plag phenocrysts. Two 1.5 cm cobalite veins. Increase in pyrite as disseminated blebs. K-spar alt. disappears.
L480542	48.9	50.9	2			S	AR	Di	Silicified Diorite	fdsp, mafics	v	50							4	0	0			0	3	4	3	4	0	1			0		1		tr	Lithology continues. At 50.6 m there is a fault associated with 20 cm of rubble/gouge and bounded by matrix supported breccia. Rock is fine grained and lighter grey in colour. AR alt increase. Magnetite drops out. Increase in qtz/carb veins.
L480543	50.9	52.8	1.9			S	QC	Di	Silicified Diorite	qtz, fdsp, mafics	v	85	v	70					2	2	3			2	3	5	2	3	1	1			1		1		tr	Lithology continues. Weak magnetite as fracture fillings. Still lighter grey grey diorite, higher sericite and clay alt. Qtz veins with moly salvages. Py as disseminated blebs and vnlts. Increase in qtz veining.
L480544	52.8	54.4	1.6			S	QC	Di	Silicified Diorite	qtz, fdsp, mafics	v	40	v	60					1	3	2			2	3	4	3	2	0	1			1		1		tr	Lithology continues. Di is lighter grey/green colour due to increase clay and sericite alt. Softer rock. 2 cm thick cobalite vein at 60 deg. Moly as qtz vein salvages and py as fracture coatings.

L480562	83.2	85.2	2	S	QC	Di	Silicified Diorite	fdsp, hornblende, mafics	v	40					1	2	1	0										tr	tr	tr	tr	Lithology continues. Decrease in potassic altn. Quartz content might be increasing to a quartz diorite.	
L480563	85.2	87.2	2	S	QC	Di	Silicified Diorite	fdsp, hornblende, mafics	v	30					1	3	1	0										tr	tr	tr	tr	Lithology continues. Tr potassic altn on joint surfaces. Tr epidote along qtz veins.	
L480564	87.2	89.1	1.9	S	QC	Di	Silicified Diorite	fdsp, hornblende, mafics	v	50					1	2	1	0										tr	tr	tr	tr	Lithology continues. Slight increase in chlorite alteration downhole. Potassic altn on fractures.	
L480565	Blank	CDN-BL-8																															
L480566	89.1	91.1	2	S	QC	Di	Silicified Diorite	fdsp, hornblende, mafics	v	30					1	2	0	0										tr	tr	tr	tr	Lithology continues. Increase in chlorite and potassic altn. Most of the feldspars are altering out. The only major vein has strong moly and cpy associated.	
L480567	91.1	93.2	2.1	S	QC	Di	Silicified Diorite	fdsp, hornblende, mafics	v	40	v	20			1	2	0	1										tr		1	0.5	0.25	Lithology continues. Potassic and chlorite altn decreasing downhole. Strong cpy and moly veins at 90.6m.
L480568	93.2	94.9	1.7	S	QC	Di	Silicified Diorite	fdsp, hornblende, mafics	v	40					1	2	0	0										tr		1	0.5	tr	Lithology continues. Slight increase in grain size. Potassic altn on joint surfaces. Moly on edges of qtz veins.
L480569	94.9	96.9	2	S	QC	Di	Silicified Diorite	fdsp, hornblende, mafics	v	40					1	2	1											tr		0.5	tr	tr	Lithology continues. Trending to finer grain downhole. Potassic altn in stron along fractures and qtz veins.
L480570	96.9	99	2.1	S	QC	Di	Silicified Diorite	fdsp, hornblende, mafics	v	40					1	1	1		2									tr	tr	tr	tr	Lithology continues. Chlorite altn increases, rock becoming more mafic. Carbonate veins are appearin again, 1/m	
L480571	99	101	2	S	QC	Di	Silicified Diorite	fdsp, hornblende, mafics	v	30					1	3	1		1									tr	tr	tr	tr	Lithology continues. Thin actinolite stringers are beginning to appear. Qtz veining appears to be following jointing angles. Original texture is being destroyed by chlorite altn.	
L480572	101	103	2	S	QC	Di	Silicified Diorite	fdsp, hornblende, mafics	v	40					2	2	1		1									tr		0.5	0.25	tr	Lithology continues. Original textyure reappearing as chlorite altn decreases. Sulfides are along fracture surfaces and qtz veins.
L480573	103	105.1	2.1	S	QC	Di	Silicified Diorite	fdsp, hornblende, mafics	v	40					2	2	2		1									tr		0.5	0.25	tr	Lithology continues. Chlorite altn increasing. Actinolite veins contain cpidotated and tr sulfides.
L480574	105.1	107.1	2	S	QC	Di	Silicified Diorite	fdsp, hornblende, mafics	v	30					2	4	2		1									tr		1	0.25	0.25	Lithology continues. Increase in qtz veining with cpy and moly. Chlorite altn comes in and out. Incr in epidote. Actinolite with carbonte salvages and cpy and epidote.
L480575	Standard	CDN-CM-12																															
L480576	107.1	109.1	2	S	QC	Di	Silicified Diorite	fdsp, hornblende, mafics	v	50					1	3	1		1									tr		0.5	tr	0.5	Lithology continues. Increase in actinolite, one setion is 10 cm thick with strong cpy and moly.
L480577	109.1	111.3	2.2	S	QC	Di	Silicified Diorite	fdsp, hornblende, mafics	v	30					2	2	1		1									1		1	0.25	0.25	Lithology continues. Increase in magnetite content, some grains up to 5mm. Chlorite alteration is dropping off. Most sulfides are within fracture surfaces.
L480578	111.3	113.2	1.9	S	QC	Di	Silicified Diorite	fdsp, hornblende, mafics	v	20					1	2	1		1									1		0.5	tr	tr	Lithology continues. Potassic alteration dropping off. Bleaching of the rouck around joints. Actinolite blebs and veins increasing.
L480579	113.2	115.4	2.2	S	QC	Di	Silicified Diorite	fdsp, hornblende, mafics	v	30					2	3	2		2									1		0.5	tr	tr	Lithology continues. Veining increases slightly, but weak sulfides in most veins. Rock is becoming more bleached out, lighter in colour around joints.
L480580	115.4	117.4	2	S	QC	Di	Silicified Diorite	fdsp, hornblende, mafics	v	30					1	2	2		2									1	tr	tr	tr	Lithology continues. Decrease in chlorite altn, original texture is becoming more visible. Actinolite veins are becoming more common are contain moly and cpy. Bleaching of the rock occurs 1-2cm around joint surfaces.	
L480581	117.4	119.5	2.1	S	QC	Di	Silicified Diorite	fdsp, hornblende, mafics	v	40					1	3	2		3									1	tr	tr	tr	Lithology continues. Chlorite altn coming in and out. Actinolite veins up to 3cm thick with cpy and moly. Potassic altn dropping off.	

L480598	144.7	146.7	2		S	QC	Di	Silicified Diorite	fdsp, hornblende, mafics	v	30	v	85						2	2	4											tr			0.5	tr		0.25	Lithology continues. Increase in K-spar alt. Decrease in magnetite and disseminated py.
L480599	146.7	148.7	2		S	QC	Di	Silicified Diorite	fdsp, hornblende, mafics	v	85								3	1	1											1		0.5	tr	tr	Lithology continues. Decrease in K-spar alt. and increase in chlorite alt. Qtz veins decrease. Still highly silicified. Decrease in grain size. Finely disseminate dpy and few small vnls.		
L480600	148.7	150.7	2		S	QC	Di	Silicified Diorite	fdsp, hornblende, mafics	v	50								2	3	1											1		0.5	tr	tr	Lithology continues. Several qtz/carb/ sulphide veins at steep angles to core axis. Few magnetite veins.		
L480601	150.7	152.7	2		S	QC	Di	Silicified Diorite	fdsp, hornblende, mafics	f	25								3	4	1											tr		0.5	0.25	0.25	Lithology continues. Blebs of cpy. Moly as fracture coatings. Leached qtz/carb/sulphide veins associated with epidote. Magnetite content decreases.		
L480602	152.7	154.7	2		S	QC	Di	Silicified Diorite	fdsp, hornblende, mafics	v	35	v	45						2	3	2												tr		0.5	0.25	0.25	Lithology continues. Still leached carb/Qtz/sulphide veins. Increase in chlorite alt. moly vnls at 35 deg. Few magnetite veins.	
L480603	154.7	156.7	2		S	QC	Di	Silicified Diorite	fdsp, hornblende, mafics	v	45	v	35						3	2	1												tr		0.5	tr	tr	Lithology continues. 60 cm section of higher alt, higher K-spar, epidote and carbonate content. Chlorite actinolite veins. Disseminated py, moly vnls.	
L480604	156.7	158.7	2		S	QC	Di	Silicified Diorite	fdsp, hornblende, mafics	v	85	v	40						2	1	2												1		0.5	tr	tr	Lithology continues. Finer grained, darker Di. More chlorite alt, higher magnetite content. At 158.7 m a 1 cm thick coarse grained qtz/calcite/ k-feld/actinolite vein at 85 deg. Some finely disseminated cpy.	
L480605	Blank	CDN-BL-8																																					
L480606	158.7	160.7	2		S	QC	Di	Silicified Diorite	fdsp, hornblende, mafics	v	30	v	70						2	1	2												1		0.5	tr	tr	Lithology continues. Highly silicified and chloritized. Leached sulphide/Qtz/carb evns. Finely disseminated py and py vnls.	
L480607	160.7	162.7	2		S	QC	Di	Silicified Diorite	fdsp, hornblende, mafics	v	30	v	55						3	0	3												1		0.5	0.25	0.25	Lithology continues. Mixed moly/ cpy vein at 30 deg. K-spar and epidote alt. associated with Qtz veins. Magnetite veins. Cpy on fracture surfaces.	
L480608	162.7	164.7	2		S	QC	Di	Silicified Diorite	fdsp, hornblende, mafics	v	45	v	85						2	1	2												1		0.5	tr	tr	Lithology continues. 2 cm thick magnetite vein at 85. epidote and k-spar alt along Qtz veins. Moly and py salvages along Qtz veins. <1mm Several thin chlorite/actinolite veins.	
L480609	164.7	166.7	2		S	QC	Di	Silicified Diorite	fdsp, hornblende, mafics	v	45								1	3	2												1		1	0.25	0.25	Lithology continues. Moly salvages on Qtz veins. Cpy salvages on Qtz veins. Sericite alt. of actinolite. Many chlorite veins. K-par alt associated with Qtz veins.	
L480610	166.7	168.7	2		S	QC	Di	Silicified Diorite	fdsp, hornblende, mafics	v	45								1	2	1												1		0.5	0.5	0.25	Lithology continues. Finely disseminated py and cpy throughout. Moly vnls. Increase in Qtz/carb veins	
L480611	168.7	170.7	2		S	QC	Di	Silicified Diorite	fdsp, hornblende, mafics	v	45	v	85						2	1	3												1		0.5	0.25	0.25	Lithology continues. Cpy associated with magnetite veins.	
L480612	170.7	172.7	2		S	QC	Di	Silicified Diorite	fdsp, hornblende, mafics	v	30	v	80						2	2	3												1		0.5	tr	tr	Lithology continues. Qtz veins with moly salvages. K-spar and epidote alt associated with Qtz veins. Mixed xchlorite/ cpy and py veins. Moly fracture coating	
L480613	172.7	174.7	2		S	QC	Di	Silicified Diorite	fdsp, hornblende, mafics	C	65	v	85						1	2	3												1		0.5	tr	tr	Lithology continues. At 174.6 section of more AR alteration, softer lighter rock, higher sericite content. Mafics almost entirely altered, plag phenocryst alt. to plag.	
L480614	174.7	176.7	2		S	AR	Di	Silicified Diorite	fdsp, hornblende, mafics	v	55								1	1	4												0		0.5	tr	tr	Lithology continues. Entire sample highly alt. by clay, sericite and Si. Hematite staining. Variation from AR alt. Di and mtz supp. Breccia. Sample appears to have undergone deformation. 15 cm Qtz vein at 174.7 m (dark Qtz, mixed with disseminated py and moly) at 55 deg.	
L480615	Standard	CDN-CM-11A																																					

L480674	280.3	282.3	2	S	EC	Di	Silicified Di	fdsp, hornblende, mafics.	v	70	v	40								2	2	3												tr	tr	tr						Lithology continues. Decrease in epidote alt. 40 cm section of moe AR alt, deformation, matrix supported breccia. Qtz veins with moly salvages.
L480675	Standard	CDN-CM-11A																																								
L480676	282.3	284.3	2	S	EC	Di	Silicified Di	fdsp, hornblende, mafics.	C	45	v	55								1	2	7																	0.25	Lithology continues. Original Di texture preserved. Quartz veining associated with K-spar alt. Contact at 45 deg with 120 cm monzonite dyke, mainly alkali fdsp. Strong moly salvages along fracture surfaces in this dyke, no magnetite in dyke.		
L480677	284.3	286.3	2	S	EC	Di	Silicified Di	fdsp, hornblende, mafics.	v	20	v	40								1	3	7																tr	Lithology continues. First 90 cm of sample is in monzonite dyke. Rest of sample is classic Di with preserved texture and thin qtz veins with k-spar salvages.			
L480678	286.3	288.3	2	S	EC	Di	Silicified Di	fdsp, hornblende, mafics.	v	35	v	75								2	3	8																tr	Lithology continues. Several steeply dipping dark qtz veins with disseminated moly and py. 50 cm section of softer lighter, Di, more AR alt. and carbonate content (felsic dyke). Hematite staining along fractures.			
L480679	288.3	290.3	2	S	EC	Di	Silicified Di	fdsp, hornblende, mafics.	f	15	v	70								2	3	9																tr	Lithology continues. Epidote alt. increasing. Tr sulphides. Moly as fracture coating.			
L480680	290.3	292.3	2	S	EC	Di	Silicified Di	fdsp, hornblende, mafics.	f	10	v	50								2	3	9																tr	Lithology continues. Moly coating on fracture at 10 deg. Strong epidote alt. blebs of cpy. Moly salvages along veins. Increase in carbonate content.			
L480681	292.3	294.3	2	S	EC	Di	Silicified Di	fdsp, hornblende, mafics.	f	10	v	85								3	3	6																tr	Lithology continues. Moly and py fracture coatings on fracture at 10 deg. Thin cpy stringers. Moly slaves on qtz veins. 70 cm section of less silicified, softer, lighter Di (more epidote and carbonate alt.) included in this section is several steeply dipping dark qtz veins mixed with disseminated pyrite and tr moly.			
L480682	294.3	295.8	1.5	S	EC	Di	Silicified Di	fdsp, hornblende, mafics.	f	20	v	30								1	2	6																tr	Lithology continues. Increase in epidote alt. Cpy along fracture surface. Moly salvages on qtz veins.			
L480683	295.8	297.2	1.4	S	EC	Di	Silicified Di	fdsp, hornblende, mafics.	v	70	f	60								1	3	5																0.25	Lithology continues. Moly as fracture coatings. Py in small vnits and disseminated. Small section of original Di texture coming through the severaly altered Di. Qtz veins highly alt. to k-spar and epidote.			
L480684	297.2	299.3	2.1	S	AR	FD	Felsic Dyke	fdsp, qtz, mafics	v	65	v	10								3	2	6																tr	Felsic dyke. Fdsp have been alt to clay. Red mineral in thin veins. Dark qtz veins. Contact at 70 deg, sharp contacts both up and down hole.. Abundant qtz/carb veins.			
L480685	Blank	CDN-BL-8																																								
L480686	299.3	301.3	2	S	AR/EC	FD/Di	Felsic Dyke/ Silicified Di	fdsp, qtz, mafics	v	75	v	15								3	4	11																0.25	First 75 cm is the continuation of the felsic dyke from above, but with thicker more abundant qtz veining, higher degree of mineralization, dark qtz veins with disseminated py, cpy and moly.. The rest of sample is the silicified Di lithology.			
L480687	301.3	303.3	2	S	EC	Di	Silicified Di	fdsp, hornblende, mafics.	v	30	v	10								2	4	6																tr	Silicified Di lithology continues. K-spar alt. along joints. Py and moly salvages along qtz veins.			
L480688	303.3	305.3	2		EC	Di	Silicified Di	fdsp, hornblende, mafics.	f	25	v	70								3	2	4																tr	Lithology continues. Decrease in K-spar alt. Increase in magnetite content.			
L480689	305.3	307.2	1.9		EC	Di	Silicified Di	fdsp, hornblende, mafics.	v	15	v	85								1	1	8																tr	Lithology continues. Di texture is mostly preserved.			
L480690	307.2	309.3	2.1		EC	Di	Silicified Di	fdsp, hornblende, mafics.	v	35	4	40								1	2	9																tr	Lithology continues. Hematite staining of fracture surfaces. Slight decrease in epidote alt.			

L480728	371.1	372.5	1.4		EC	Di	Silicified Di	fdsp. hornblende, mafics	v	30	v	55					1	2	3		6		3	1	5	1	4	4	2								tr		tr		tr		tr	Lithology continues, increase in carbonate content and qtz/carb veins all dipping 60 deg. Decrease in sulphides.		
L480729	372.5	373.4	0.9		AR	FD	Felsic Dyke	fdsp, qtz, mafics	v	50							0	5	10		5		1	4	4	4	1	1	3										tr		tr		Felsic dyke. Abundant qtz veining. Some matrix supported brecciation. soft. Light coloured. Fdsp pheno have alt to clay and sericite. Monzonite composition? Calcite leaching.			
L480730	373.4	374.3	0.9		EC	Di	Silicified Di	fdsp. hornblende, mafics	v	45							1	1	5		2		3	1	5	1	4	4	1											tr		tr		tr		Silicified Di lithology continues. Highly alt. Slight increase in K-spar alt. tr sulphides.
		EOH																																												

BC-11-02

PROJECT: BING
 ID Hole: PB-11-02
 Core Inclination: -60
 Azimuth: 90
 Length: 394.7m

Start Date: 29-Jun-11
 End Date: 6-Jul-11
 Size: HQ 0- NQ

Drill Contractor: Black Hawk

Collar: UTM (NAD83)

UTM_E: 668170
 UTM_N: 6471360
 UTM_Zone: 8
 Elev: 1428 m

Paget Minerals Corp.

Geologist: _____

Date Log completed: Pg _____ of _____

Sample Number	From (m)	To (m)	Length (m)	Geology - Lithology			Lithology	Rock type/texture	Rock composition	Structure						Veins/1m					Alteration							Mineralization				Description							
				Graph Log	Redox OI/MS	Alter. Code				Rock Code	Type (F, f, B, v, C)-Angle						Breccia	Sulfide	Qtz-Sulf/Ox	Quartz	Mntqtz	Other	biotite	K-fspar	Sericite	Silica	Clays	Chlorite	Epidote	Calcite	Other		Oxide / Limonite	Magnetite %	Other: Cu, Mn, etc.	Pyrite	Cpy	Bornite	Moly
											Fault, fract, bed, vnl, contact																												
	0	14.9	14.9				OB																												Ore__py, cpy, bor, cv, sph, gal; Structure__ Bx, F, f, V, v, B; Other__ stk, dsm, prvs, mtz, slvg.				
L480309	14.9	16.2	1.3	M	QS	Di	Silicified Diorite	flds/mafics	v	30	f	0						1	2	1	1														Overburden comprised of mainly diorite and rubble core. Dark grey, medium grained silicified diorite. moderate amounts of oxidation along fractures. Cross cutting quartz veins with moderate pyrite and tr chalc. Tr epidote along veins. Tr magnetite.				
L480310	16.2	17.9	1.7	M	QS	Di	Silicified Diorite	flds/mafics	v	0	f	5						2	1	0	1														Lithology continues. Thick quartz vein running sub parallel to core axis with moderate py and tr chalc. Weak veins of magnetite. Similar oxidation. Tr moly on edge of qtz vn.				
L480311	17.9	19.8	1.9	M	QS	Di	Silicified Diorite	flds/mafics	v	0	f	60						2	3	1															Lithology continues. Sulphide filled fractures continue to run parallel to core axis. Tr cpy and moly in fractures. Increase in potassic alteration. Several repeated fractures at 60 deg				
L480312	19.8	21.8	2	M	QS	Di	Silicified Diorite	flds/mafics	f	0	v	50						1	4	2															lithology continues. Radial actinolite in fracture. Py and cpy mainly vein controlled. Some oxidation in fractures. Ep. Associated with veins.				
L480313	21.8	23.8	2	M	QS	Di	Silicified Diorite	flds/mafics	v	25								2	3	1															Lithology continues. Potassic alteration decreases, associated mainly just along qtz veins. Increase in chlorite alteration and actinolite. Magnetite increases.				
L480314	23.8	25.5	1.7	M	QC	Di	Silicified Diorite	flds/mafics	v	0	f	0						2	4	3															Lithology continues. Qtz sulphide vein running parallel to sub parallel to core axis. Fractures also running parallel to core. 3 cm thick qtz vein running parallel to core associated with K-spar alt. Some qtz/ carb veins				
L480315	CDN-CM-11A																																						
L480316	25.5	27.4	1.9	S	QC	Di	Silicified Diorite	flds/mafics	v	0								1	6	1															Lithology continues. Qtz/carb veins. Strong actinolite and chlorite alteration. Epidote along veins. Some oxidation along fractures. 3 cm thick qtz vein parallel to core axis associated with py and ep.				
L480317	27.4	29.2	1.8	S	QC	Di	Silicified Diorite	flds/mafics	f	40								1	5	1															Lithology continues. Qtz/carb veins. Py occurs in fractures and qtz sulphide veins and as disseminated blebs.				
L480318	29.2	31.4	2.2	S	QC	Di	Silicified Diorite	flds/mafics	v	0	v	10						5	4	1															Lithology continues. Calcite vein at 10 deg. Strong cpy occurrence on one fracture. Actinolite and chlorite still strong.				

L480319	31.4	33.6	2.2	S	QC	Di	Silicified Diorite	flds/mafics	v	10				4	5	0	1	3	5	4	1							2		3	tr		Lithology continues. Calcite veins continue to run through core at 10 deg. Some oxidation in fractures. Strong actinolite and chlorite alt.									
L480320	33.6	35.7	2.1	S	QC	Di	Silicified Diorite	flds/mafics	v	0	v	20					3	5	1	1	3	5	4	1							2		4	1	tr	Lithology continues. Tr moly and cpy in 1 cm thick qtz vein running sub parallel to core axis. Calcite vein at 20 deg with py along edges. Finely disseminated cpy. Some potassic alt. associated with qtz veins.						
L480321	35.7	37.4	1.7	S	QC	Di	Silicified Diorite	flds/mafics	v	30						2	3	2	2	3	5	4	1							2		3	tr	Lithology continues. Potassic alt. picks up with qtz veins. Cpy along edges of 3 cm thick qtz vein at 30 deg.								
L480322	37.4	39.5	2.1	S	QC	Di	Silicified Diorite	flds/mafics	v	40						1	3	3	2	3	5	4	1							2		3	1	tr	Lithology continues. Qtz veins with salvages of potassic alt. At 38.4m there is a 5 cm long cpy bleb mixed with py. That is also associated with strong magnetite.							
L480323	39.5	41.4	1.9	S	QC	Di	Silicified Diorite	flds/mafics	v	35							3	2	1	2	3	5	4	1								2		3	tr	Lithology continues. Magnetite in veins. Very fine py.						
L480324	41.4	43.7	2.3	S	QC	Di	Silicified Diorite	flds/mafics	v	85							3	3	3	1	2	4	5	1								2		2	tr	Lithology continues. Cpy and py in 1mm vnits. Ep along veins. At 42.0 m there is less silicic alt. and more sericite, actinolite and chlorite alt. The rock is finer grained and more mafic. Calcite veins with salvages of chlorite, actinolite and magnetite.						
L480325	Blank																																									
L480326	43.7	45.7	2	S	QC	Di	Silicified Diorite	flds/mafics	f	20										1	2	4	5	1								2		2	tr	Lithology continues. Cpy and py in 1mm vnits. Ep along veins. Rock is still finer grained with less visible plag phenocrysts. Calcite veins.						
L480327	45.7	47.9	2.2	S	QC	Di	Silicified Diorite	flds/mafics	v	20	v	15									1	2	4	5	1								2		2	tr	Lithology continues. Moly and chlorite in vein at 15 deg. Cpy vnits. Most sulphide veins have shallow angle. Qtz/ carb veins.					
L480328	47.9	50.1	2.2	S	QC	Di	Silicified Diorite	flds/mafics	v	25										1	3	5	4	1									2		2	tr	Lithology continues. Moly and cpy salvages in 3cm qtz vein at 25 deg. Plag phenocrysts reappear, coarser grains and silicification increases.					
L480329	50.1	52.1	2	S	QC	Di	Silicified Diorite	flds/mafics	v	25											1	3	5	4	1	1							2		2	tr	Lithology continues. Two Qtz/ carb/ cpy vein at 25 deg. Magnetite filling fractures.					
L480330	52.1	54.2	2.1	S	QC	Di	Silicified Diorite	flds/mafics	v	50											1	3	5	4	1									2		2	tr	Lithology continues. Py mainly associated with qtz/ carb veins. Potassic alt. salvages along qtz veins				
L480331	54.2	56.4	2.2	S	QC	Di	Silicified Diorite	flds/mafics	v	45											1	3	5	4	1									3		3	tr	Lithology continues. Strong py for 6cm at 55.2 m. Magnetite in veins.				
L480332	56.4	58.2	1.8	S	QC	Di	Silicified Diorite	flds/mafics	v	40	v	20									2	4	3	1											3		2	tr	Lithology continues. Chlorite and actinolite decreases as silicification increases. Increase is flds phenocrysts. Chlorite filling fractures.			
L480333	58.2	60.2	2	S	QC	Di	Silicified Diorite	fdsp/mafics	v	65											3	3	5	4	1										3		2	tr	Lithology continues. Potassic alt along qtz veins. Finer grained with fewer fdsp phenos. Py occurs mainly as disseminated blebs and in small veinlets.			
L480334	60.2	62.2	2	S	QC	Di	Silicified Diorite	fdsp/mafics	v	25											2	2	1													3		2.0	tr	Lithology continues. Qtz/carb vein with moly and tr chalco.		
L480335	Standard	CDN-CM-12																																								
L480336	62.2	64.1	1.9	S	QC	Di	Silicified Diorite	fdsp/mafics	v	60																												Lithology continues. Switched from HQ to NQ and lost recovery resulting in rounded gravel sized pieces. Abundant actinolite.				
L480337	64.1	66.1	2	S	QC	Di	Silicified Diorite	fdsp/mafics													3	3	2													3		2.0	tr	Lithology continues. Qtz veins with pyrite disseminated throughout with k-spar selvages. Fdps phenos increase. Mm magnetite veins. Chalco occurs as large blebs throughout.		
L480338	66.1	68.1	2	S	QC	Di	Silicified Diorite	fdsp/mafics	v	45											2	3	4														3		2	tr	Lithology continues. Vein of chlorite/actinolite with small blocks of wall rock of diorite within being crosscut by small pyrite veinlet. Qtz veins with k-spar alt as selvages.	
L480339	68.1	70.1	2	S	QC	Di	Silicified Diorite	fdsp/mafics	v	40											2	5	2														3		2	tr	Lithology continues. Moly disseminated throughout with small veinlets. Qtz veins with k-spar selvages.	
L480340	70.1	72.1	2	S	QC	Di	Silicified Diorite	fdsp/mafics	v	45	f	25																										3		5.0	tr	Lithology continues. Slight increase in pyrite veins.

L480341	72.1	74.1	2		S	QC	Di	Silicified Diorite	fdsp/mafics	v	45								3	3	2										3		3.0	tr		tr	Lithology continues. K-spar alt along qtz veins with minor replacement zones in host rock. Moly disseminated in qtz veins as small blebs and also as small veinlets.					
L480342	74.1	76.1	2		S	QC	Di	Silicified Diorite	fdsp/mafics	v	60								3	4	4										3		4.0	1	tr	Lithology continues. 2mm vein of chalco. Moly disseminated throughout.						
L480343	76.1	78.1	2		S	QC	Di	Silicified Diorite	fdsp/mafics	v	45								2	1	3										3		2	tr	tr	Lithology continues. K-spar alt along qtz vein with minor replacement zones.						
L480344	78.1	80.1	2		S	QC	Di	Silicified Diorite	fdsp/mafics										1	3	2										3		3.0	tr	tr	Lithology continues. Small veinlets of chalco and moly. Late stage carb veins cross cutting other features and structures in core.						
L480345	Blank	CDN-BL-8																																								
L480346	80.1	82.1	2		S	QC	Di	Silicified Diorite	fdsp/mafics	v	0	F	60						4	2	1											3		2	tr	tr	Lithology continues. Small veinlets of chalco. Fine grained with few fdsp phenos. End of sample is at contact with fault gouge at 60 degrees to core axis.					
L480347	82.1	84.1	2		S	QC	Di	Silicified Diorite	fdsp/mafics	F	60								2	2	2										3		2	tr	tr	Lithology continues. Fault gouge approx. 40cm. Chlorite/actinolite veins. 2mm chalco veinlets.						
L480348	84.1	86.1	2		S	QC	Di	Silicified Diorite	fdsp/mafics										3	2	1										3		2	tr	tr	Lithology continues. Sericite along fractures. 1-2mm veinlets of chalco.						
L480349	86.1	88.1	2		S	QC	Di	Silicified Diorite	fdsp/mafics	v	10								2	3	1										3		2	5	4	1	tr	tr	Lithology continues. Qtz veins sub-parallel to core axis with disseminated moly and k-spar selvages with minor zones of replacement. 1mm carb veins cross cutting qtz veins.			
L480350	88.1	90.1	2		S	QC	Di	Silicified Diorite	fdsp/mafics	v	35								3	2	2										4		2	5	4	1	tr	tr	Lithology continues. Increase in size of qtz veins and k-spar alt. Decrease in magnetite and pyrite. Small veinlets of moly. Clay along fractures.			
L480351	90.1	92.1	2		S	QC	Di	Silicified Diorite	fdsp/mafics	f	15								3	3	4										4		2	5	4	2	tr	tr	Lithology continues. Continuation of larger qtz veins and k-spar alt with a decrease in magnetite and pyrite.			
L480352	92.1	94.1	2		S	QC	Di	Silicified Diorite	fdsp/mafics	v	45								2	3	2										4		3	5	4	1	1	tr	tr	Lithology continues. Gradual decrease in qtz veins and increase in magnetite and pyrite. Slight decrease in overall silicification with increase in sericite(?). Late stage carb veins.		
L480353	94.1	96.1	2		S	QC	Di	Silicified Diorite	fdsp/mafics	f	80	v	70						2	1	2		10								4		2	5	4	2	2	tr	tr	Switch logging to Chris Weldon. Lithology continues. 10 qtz/carb veins per meter, typically less than 1mm wide. Qtz veins are kspar altered. Chalco associated with epidoted on qtz vein selvages.		
L480354	96.1	98.1	2		S	QC	Di	Silicified Diorite	fdsp/mafics	v	40								1	2	2		3								4		2	5	4	2	1	tr	tr	Lithology continues. Brecciated quartz vein with strong chlorite alteration within matrix. Qtz/carb veins less abundant but still occurring.		
L480355	Standard	CDN-CGS-23																																								
L480356	98.1	100.1	2		S	QC	Di	Silicified Diorite	fdsp/mafics	v	40								2	1	1		3									4		2	5	4	2	1	tr	tr	Lithology continues. Magnetite associated with chlorite alteration. Slight increase in potassic alteration resulting in lighter rock. Appears to be a 10cm thick silicified shear zone/breccia with increased py, cpy and epidote.	
L480357	100.1	102.1	2		S	QC	Di	Silicified Diorite	fdsp/mafics	v	50								3	2	2		1									4		1	5	4	2	1	tr	tr	Lithology continues. Increase in potassic alteration. Blebs with tr moly and moly along qtz vein fractures. Mnt with chlorite alteration. Quartz carb brecciated vein for 1cm with abundant potassic alteration on outside.	
L480358	102.1	104.1	2		S	QC	Di	Silicified Diorite	fdsp/mafics	v	80								2	1	1		2									4		1	5	4	2	1	tr	tr	Lithology continues. One good vein with abundant cpy and py. Moderate moly with one qtz vn.some blebs of strong kspar altn.	
L480359	104.1	106.1	2		S	QC	Di	Silicified Diorite	fdsp/mafics	c	20								1	1	1											4		1	5	1	4	1	tr	tr	Lithology continues. Decrease in sulphides and magnetite with slight increase in kspar altn. Cross cutting qtz vn over kspar altd qtz/carb vein. Tr clay along fractures.	
L480360	106.1	107.9	1.8		S	QC	Di	Silicified Diorite	fdsp/mafics	v	40	f	40						1	1	1											4		1	5	1	4	1	1	tr	tr	Lithology continues. 2cm breccia with qtz/carb veins. Decrease in mnt. Tr clay along fracture surface.
L480361	107.9	109.8	1.9		S	QC	Di	Silicified Diorite	fdsp/mafics	v	40	f	10						1	1	1		1									4		1	5	1	4	1	1	tr	tr	Lithology continues. 8cm felsic dyke at 109.7m with strong kspar altn and a moly bearing qtz vn cutting through it. Strong carbonate along fracture running parallel to core axis

L480382	143.6	145.7	2.1		QC	Di	Silicified Diorite	fdsp/mafics	v	10	v	65						2	4	3		2		4	1	5	1	3	1	1			1		1	tr		tr	Lithology continues. Alt same as above. Moly/ qtz veins at 10 deg. Repeated 65 deg qtz/ sulphide veins.
L480383	145.7	147.6	1.9		QC	Di	Silicified Diorite	fdsp/mafics	v	75	v	25						3	4	4		2		4	1	5	1	3	1	1			1		1	tr	tr	Lithology continues. Cpy vnlt. Qtz/moly vein at 75 deg. Some magnetite filling fractures.	
L480384	147.6	149.7	2.1		QC	Di	Silicified Diorite	fdsp/mafics	v	30								2	4	3		2		4	1	5	1	3	1	1			1		1	tr	tr	Lithology continues. 3 cm thick qtz vein with visible moly along edges at 30 deg. Cpy vein controlled.	
L480385	Blank	CDN-BL-8																																					
L480386	149.7	151.6	1.9		QC	Di	Silicified Diorite	fdsp/mafics	v	55	v	70	v	85				3	5	3		2		3	1	5	1	3	1	1			1		1	tr	tr	Lithology continues. Potassic alt. decreases. Mixed cpy, moly and qtz veins ranging from 55 to 70 deg. Five 0.5 mm thick cpy vnlt crosscutting strong magnetite vein (85 deg).	
L480387	151.6	153.6	2		QC	Di	Silicified Diorite	fdsp/mafics	v	10	v	75						2	4	2		3		3	2	5	1	3	1	1			1		1	tr	tr	lithology continues. Coarser grains, increase in feldspar phenocrysts. Slight increase in cpy mineralization, and disseminated py. Moly vein at 10 deg. 2 cm thick magnetite vein at 75 deg.	
L480388	153.6	155.7	2.1		QC	Di	Silicified Diorite	fdsp/mafics	v	65	v	80						2	5	2		2		2	2	5	1	3	1	1			2		1	tr	tr	Lithology continues. Qtz sulphide veins mainly at 65 deg. Steeply dipping cpy vnlt. K-spar alt. decreases as magnetite increases.	
L480389	155.7	157.8	2.1		QC	Di	Silicified Diorite	fdsp/mafics	v	65	f	20						3	4	2		1		2	2	5	1	3	1	1			2		1	1	tr	Lithology continues. Cpy vnlt at 65 deg. Fracture at 20 deg with calcite, sericite and clay along fracture surface.	
L480390	157.8	159.8	2		QC	Di	Silicified Diorite	fdsp/mafics	C	45	C	55						4	3	3		1		3	2	5	1	3	1	1			2		1	1	tr	Lithology continues. One FP dike at 158.1 m, 11 cm thick, contact at 45 deg. Second FP dyke at 158.3 m, 15 cm thick, contact at 55 deg. (FP- 1 mm to 4 mm fold. Phenocrysts, stonger cpy in FP. Highly silicified and potassic alt.)	
L480391	159.8	161.8	2		QC	Di	Silicified Diorite	fdsp/mafics	v	10								2	4	3		2		3	2	5	1	3	1	1			2		1	1	tr	Lithology continues. Moly and cpy mixed with qtz veins. Some disseminated py. AR along fractures.	
L480392	161.8	163.9	2.1		QC	Di	Silicified Diorite	fdsp/mafics	C	25	v	65						2	3	3		4		4	2	5	1	3	1	1			1		1	1	tr	Lithology continues. Shear zone at 163 m with M supported breccia (25 deg contact). silicified. Qtz veing with moly and K-spar salvages. Actinolite present. Disseminated cpy. AR along fractures.	
L480393	163.9	165.8	1.9		QC	Di	Silicified Diorite	fdsp/mafics	v	15								3	2	4		10		4	2	5	1	3	1	1			1		1	tr	tr	Lithology continues. Many thin fractures filled with carbonate and qtz forming network. Moly along qtz veins.	
L480394	165.8	167.9	2.1		QC	Di	Silicified Diorite	fdsp/mafics	vnlt	20	f	25						3	4	4		3		4	2	5	1	3	1	1			>1		1	tr	tr	Lithology continues. Increased potassic alt. Moly vnt at 20 deg. Strong moly along f at 25 deg. Shear zone at 166.4 m with strong AR alt.	
L480395	Standard	CDN-CGS-23																																					
L480396	167.9	169.9	2		AR	Di	Silicified Diorite	fdsp/mafics	v	60	v	90						2	3	3		30		4	3	4	3	2	1	2			0		1	tr	tr	Lithology continues. AR becomes more prominent. Clay and sericite alt. increase. Di is softer and lighter in colour. Silicification decreases. Carbonate increases. Many qtz/veins steeply dipping (60-90 deg)	
L480397	169.9	171.9	2		QS	Di	Silicified Diorite	fdsp/mafics	v	25								1	3	1		6		4	3	4	3	2	1	2			1		1	tr	tr	Lithology continues. First 85 cm of sample is more silicified, less AR. Rest of sample Alt mainly same as above, Softer, lighter Di. 2.5 cm thick qtz veins with visible moly mainly on edges at 25 deg. Dissminated cpy and py. Magnetite in QC diorite section.	
L480398	171.9	174	2.1		QS	Di	Silicified Diorite	fdsp/mafics	v	15								2	3	3		40		4	4	4	2	4	1	2			1		tr	tr	tr	Switch logging to Eric. Lithology continues. Diorite experienced greater alteration (sericitic), becoming lighter in color. 25cm section of clast supported breccia. Decrease in silicification and increase in sericite alt.	
L480399	174	176.1	2.1		QS	Di	Silicified Diorite	fdsp	v	15	v	20						4	3	3		10		4	4	3	4	4	1	3			0		tr	tr	Lithology continues. Diorite still leucocratic. Argillic alt increasing with decreasing sericitic alt. qtz veins with k-spar selvages at high angles to core axis. Fine grained sulphide/Qtz veins.		
L480400	176.1	178.1	2		QS	Di	Silicified Diorite	fdsp	f	35								2	2	2		10		4	4	4	4	3		3			0		tr	tr	Lithology continues. Still light colored becoming more siliceous towards end of sample. Sub-parallel veins of fg sulphides. Calcite veins at high angle to core axis.		
L480401	178.1	180.1	2		QS	Di	Silicified Diorite	fdsp/mafics	v	45								2	3	2		5		4	4	4	3	3		3			0		tr	tr	Lithology continues. Still light colored. Increase in silicification. Increase in fdsp phenos. K-spar alt along veins and replacement of host rock.		

L480423	217.9	220	2.1		QC	Di	Silicified Diorite	fdsp/mafics	v	50						1	2	1						4	2	5	1	3	1	1			1		tr	tr		tr	Lithology continues. Bleb of moly 1cm at 219.5m. Small dykes of qtz monz and potassic altn along joint surfaces.													
L480424		220	222	2		QC	Di	Silicified Diorite	fdsp/mafics							1	1	1							4	2	5	1	3	1				1		tr	tr		tr	Lithology continues. Decreased py,												
L480425	Blank	CDN-BL-8																																																		
L480426		222	224	2		QC	Di	Silicified Diorite	fdsp/mafics							1	1	1							4	2	5	1	3	1				1		tr	tr		tr	Lithology continues. Sulfides confined to fracture surfaces. Potassic halos on joint surfaces.												
L480427		224	226	2		QC	Di	Silicified Diorite	fdsp/mafics	v	50					0	2	3							4	2	5	1	3	1				1			1.0	tr		tr	Lithology continues. Increase in qtz veins, some with associated py, cpy and moly. 5cm qtz monz dyke at 225.8											
L480428		226	228	2		QC	Di	Silicified Diorite	fdsp/mafics	v	60					0	1	2							4	2	5	1	3	1				1				tr	tr		tr	Lithology continues. Becoming coarser grained and chlorite alteration is confined to fracture surfaces. Sulphide content increases with increased chlorite altn.										
L480429		228	230	2		QC	Di	Silicified Diorite	fdsp/mafics	C	60	C	60			1	2	2							4	2	5	1	3	1				1			1.0	tr		tr	Lithology continues. 40cm qtz monz dyke at 228.15m. Mineralization increases with increased chlorite altn.											
L480430		230	232	2		QC	Di	Silicified Diorite	fdsp/mafics	F	70					0	1	2							4	2	5	1	3	1				1				tr	tr		tr	Lithology continues. Random 1-3cm qtz monz dykes with no specific orientation. Weak sulfides, most on fracture surfaces.										
L480431		232	234.1	2.1		QC	Di	Silicified Diorite	fdsp/mafics							0	0	1							4	2	5	1	3	1				1					tr			tr	Lithology continues. Possible xenolith of greenstone.									
L480432		234.1	236.1	2		QC	Di	Silicified Diorite	fdsp/mafics							1	1	2				1			4	2	5	1	3	1				1						tr		tr	Lithology continues. Increase in chlorite altn where material has a sheared appearance. Calcite veins appearing again.									
L480433		236.1	238	1.9		QC	Di	Silicified Diorite	fdsp/mafics	v	70					1	1	1	1						4	2	5	1	3	1				1						tr	tr		tr	Lithology continues. 1cm quartz vein with abundant magnetite within. Small zones where sericite altn increases.								
L480434		238	240.1	2.1		QC	Di	Silicified Diorite	fdsp/mafics	b	40					0	1	1							4	2	5	1	3	1				1						tr	tr		tr	Lithology continues. Diorite appears to have a weak foliation at 40 degrees. Grain size increases to coarse grained for this run.								
L480435	Standard	CDN-CM-12																																																		
L480436		240.1	242	1.9		QC	Di	Silicified Diorite	fdsp/mafics	v	60					0	1	0							4	2	5	1	3	1				1							tr	tr		tr	Lithology continues. Some qtz monzonite dykes are becoming qtz/flds phyric. Only one visible qtz vein with moderate moly. Tr disseminated py and cpy.							
L480437		242	244	2		QC	Di	Silicified Diorite	fdsp/mafics	v	10					0	0	1				2			4	2	5	1	3	1	1				1							tr			tr	Lithology continues. Very weak sulfides, just trace disseminated py. One qtz vein has strong kspar salvages, other one is unaltered. Chlorite alteration coming in and out. Qtz/carb veins appearing again.						
L480438		244	246.2	2.2		QC	Di	Silicified Diorite	fdsp/mafics							0	1	0				1			4	2	5	1	4	1	1				1								tr		tr	Lithology continues. Increase in chlorite altn. Try py and moly with only qtz vein. Potassic altn along joint surfaces.						
L480439		246.2	248.2	2		QC	Di	Silicified Diorite	fdsp/mafics	f	10					0	2	1				1			4	2	5	1	4	1	1				1								tr		tr		tr	Lithology continues. Tr clay and dacite altn along set of fractures. Strong chlorite altn persists.				
L480440		248.2	250.2	2		QC	Di	Silicified Diorite	fdsp/mafics	v	60					0	1	2				1			4	2	5	1	4	1	1				1										tr		tr	Lithology continues. 5cm qtz vein at 248.2m with no apparent mineralization. Trace disseminated pyrite and along fracture surfaces.				
L480441		250.2	252.2	2		QC	Di	Silicified Diorite	fdsp/mafics	v	70					0	0	2							4	2	5	1	4	1				1												tr		tr	Lithology continues. Slight decrease in chlorite altn, increase in potassic altn. 2 qtz veins are displaying a 3cm offset			
L480442		252.2	254.2	2		QC	Di	Silicified Diorite	fdsp/mafics	v	60					0	0	2							4	2	5	1	4	1				1												tr		tr		tr	Lithology continues. Increasing potassic altn. Fine disseminated py and tr moly blebs.	
L480443		254.2	256.2	2		QC	Di	Silicified Diorite	fdsp/mafics	v	60					0	0	3				2			4	2	5	1	4	1	1				1												tr		tr		tr	Lithology continues. Blebby pyrite with tr epidote associated. Mod potassic altn throughout.
L480444		256.2	258.2	2		QC	Di	Silicified Diorite	fdsp/mafics	v	50	F	50			1	3	1				2			4	2	5	1	4	1	1				1												tr		tr		tr	Lithology continues. Switch logging to Kayla. Lithology continues. 6.5 cm thick qtz vein at 50 deg with moly along edges and pyrite running through center. Fault at 50 deg at 256.67 m. associated with 22 cm of soft, clay./carbonate rich sheared Di.

L480487		330	332.1	2.1			QS	QD	Silicified Qtz Diorite	qtz/fdsp/bio/hnbl											1			4	1	5	1		1	1						tr			tr					Lithology continues. Slight increase in mafics, mostly biotite. Potassic altn on joint surfaces.								
L480488		332.1	333.9	1.8			QS	QD	Silicified Qtz Diorite	qtz/fdsp/bio/hnbl												1			4	1	5	1	1	1	1							tr								Transitioning to a zone of increased potassic and chlorite altn. Has the texture of a quartz diorite for most part, possibly some xenoliths of greenstone. Tr mnt. Weak sulfides						
L480489		333.9	335.8	1.9			QS	QD	Silicified Qtz Diorite	qtz/fdsp/bio/hnbl									1	1	0				4	1	5	1	2	1	2									tr			0.25	tr			increase in potassic altn. Increase in chlorite content, possibly some xenoliths of greenstone. Grain size is varying from fine to coarse many times. Incr in cpy.					
L480490		335.8	337.8	2			QS	QD	Silicified Qtz Diorite	qtz/fdsp/bio/hnbl	v		45						0	1	2				5	1	5	1	2	1	1															same as above. Chlorite and potassic altn coming in and out. Tr sulfides. Increase in qtz veins.						
L480491		337.8	339.8	2			QS	QD	Silicified Qtz Diorite	qtz/fdsp/bio/hnbl									0	0	1				4	1	5	1	2	1	1															same as above. Chlorite and potassic altn coming in and out. Tr sulfides. Increase in qtz veins.						
L480492		339.8	341.6	1.8			QS	QD	Silicified Qtz Diorite	qtz/fdsp/bio/hnbl									0	0	1				4	1	5	1	1	1	1																quartz diorite. Alteration is becoming weaker at the end of the section. Quartz content increasing.					
L480493		341.6	343	1.4			QS	QD	Silicified Qtz Diorite	qtz/fdsp/bio/hnbl	v		60								1				3	1	5	1	2	1																15cm of strong chlorite surrounding a 2cm qtz vein, almost has the appearance of a dyke. Rest of the run is weakly potassically altd qtz diorite.						
L480494		343	344.9	1.9			QS	QD	Silicified Qtz Diorite	qtz/fdsp/bio/hnbl	C		90	C	90				1	0	1				4	1	5	2	2	2	2																possible xenolith of greenstone from 343 to 343.4m with chlorite altn and a potassically altn vein with cpy cutting through it. 10cm section with numerous qtz/carb veins and strong altn to clay.					
L480495	Standard		CDN-CM-12																																																	
L480496		344.9	347.1	2.2			QS	QD	Silicified Qtz Diorite	qtz/fdsp/bio/hnbl									0	0	1				4	2	5	1	1	1																				Coarse grained quartz diorite trending towards increased potassic and chlorite altn downhole. Xenolith of country rock, probably greenstone sediments, are scattered within. Very weak mineralization		
L480497		347.1	349.4	2.3			QS	QD	Silicified Qtz Diorite	qtz/fdsp/bio/hnbl	F		40						0	0	0				5	2	5	2	2	1	2																		Fault zone at 347.3m that has turned to clay and chlorite. Increase in qtz/carb vnlts. Alteration is becoming pervasive with potassic and chlorite destroying original texture.			
L480498		349.4	351.5	2.1			QS	QD	Silicified Qtz Diorite	qtz/fdsp/bio/hnbl	F		40						0	0	1				5	1	5	2	3	1	2																		Fault zone at 351m for 40cm. Original diorite texture returns sporadically, but most is pervasively potassic altered and mod chlorite altered. Tr disseminated py and little veining.			
L480499		351.5	353.5	2			QS	QD	Silicified Qtz Diorite	qtz/fdsp/bio/hnbl									0	0	2				5	1	5	1	2	1	2																		Strong potassic altn, could be called a quartz monzonite also, but not sure if the kspar is primary or a secondary altn. Less than 1mm quartz/carb veins occur 2-3/m. tr quartz veining with no sulfides.			
L480500		353.5	355.3	1.8			QS	QD	Silicified Qtz Diorite	qtz/fdsp/bio/hnbl									0	0	2				5	1	5	1	2	1	1																			Same as above with strong potassic altn. Very little mineralization. Some biotite books are visible and on their way to chlorite.		
L480501		355.3	357.5	2.2			QS	QD	Silicified Qtz Diorite	qtz/fdsp/bio/hnbl	v		20						0	1	1				5	1	5	1	2	1	1																		Lithology continues. Strong potassic altn and most of the mafics have altered to chlorite. One qtz vein has tr cpy and moly on the edges.			
L480502		357.5	359.6	2.1			QS	QD	Silicified Qtz Diorite	qtz/fdsp/bio/hnbl									0	0	1				5	1	5	1	2	1	1																		Lithology continues. Strong potassic altn and most of the mafics have altered to chlorite. Moderate actinolite associated with a 3cm qtz bleb. Weak mineralization.			
L480503		359.6	361.7	2.1			QS	QD	Silicified Qtz Diorite	qtz/fdsp/bio/hnbl	v		70						0	0	1				4	1	5	1	2	1	1																			Lithology continues. Potassic chlorite altn dropping off. Original texture becoming more visible. Rock is becoming more felsic and the biotites and hornblendes are just starting to alter to chlorite.		
L480504		361.7	363.8	2.1			QS	QD	Silicified Qtz Diorite	qtz/fdsp/bio/hnbl	C		80	C	80				0	0	0				4	1	4	1	3	1	1																			Lithology continues. There is a 60cm section that is heavily chlorite altered and not as silicified as the rest of the unit, almost appears as a dyke or a later stage intrusion that was not subject to the silicification.		
L480505	Blank		CDN-BL-8																																																	
L480506		363.8	365.8	2			QS	QD	Silicified Qtz Diorite	qtz/fdsp/bio/hnbl									0	0	2				4	1	5	1	1	1	1																					Lithology continues. Decreased potassic and chlorite altn. Original texture very visible. V.weak mineralization

BC-11-03

PROJECT: BING
 ID Hole: PB-11-03
 Core Inclusion: -60
 Azimuth: 90
 Length: 300m

Start Date: 18-Jul-11
 End Date:
 Size: HQ 0- NQ

Drill Contractor:

Collar: UTM (NAD83)
 UTM_E: 668428
 UTM_N: 6470839
 UTM_Zone: 8
 Elev: 1333

Geologist:
 Date Log completed:
 Pg _____ of _____

Sample Number	From (m)	To (m)	Length (m)	Geology - Lithology	Redox O/M/S	Alter. Code	Rock Code	Lithology	Rock composition	Structure						Veins/1m					Alteration								Mineralization					Description																	
				Graph Log						Type (F, f, B, v)-Angle						Breccia	Sulfide	Qtz-Sulf/Ox	Quartz	Mnt-qtz	Other	biotite	K-fspar	Sericite	Silica	Clays	Chlorite	Epidote	Calcite	Other	Oxide / Limonite	HGJ Ratio	Magnetite %		Other: Cu, Mn, etc.	Sulfides	Pyrite	Cpy	Bornite	Moly											
										1	<	2	<	3	<																	0-5	J_H_G						Ore__py, cpy, bor, cv, sph, gal; Structure__ Bx, F, f, V, v, B; Other__ stk, dsm, prvs, mtz, slvg.												
	0	6	6				OB																															Overburden													
L480731	6	7.9	1.9	S	EC	Di	Silicified Diorite	fdsp, mafics	f	20	v	40					2	1	1		1															tr	tr							Silicified Diorite: dark grey diorite, original texture destroyed, severely alt, fine grained. Tr sulphides, py as salvages on qtz/carb veins							
L480732	7.9	10.3	2.4	S	EC	Di	Silicified Diorite	fdsp, mafics	v	30	f	45					3	2			4																tr	tr	tr					Lithology continues. Oxide staining on fracture surfaces. Beginning to pick up small blebs of cpy. Moly salvages on qtz veins. Trace K-spar alt. increase in qtz carb veins.							
L480733	10.3	11.6	1.3	S	EC	Di	Silicified Diorite	fdsp, mafics	v	20							1	1	2		1																0		tr					Lithology continues. Mostly broken core and rubble. Thin moly vnlt.							
L480734	11.6	13.7	2.1	S	EC	Di	Silicified Diorite	fdsp, mafics	v	25	v	35					2	1	2		3																tr	tr	tr					Lithology continues. Small section of AR alt, softer Di. Cpy and moly salvages on qtz veins. Increase in sulphides in the Ar alt. sections.							
L480735	Standard	CDN-CGS-23																																																	
L480736	13.7	15.6	1.9	S	EC	Di	Silicified Diorite	fdsp, mafics	v	15							2	2	3		4																		tr		1	tr					Lithology continues. Slight increase in py. Increase in chlorite alt. magnetite confined to fracture fillings. Thin moly vnlt. Cpy and py salvages on qtz veins.				
L480737	15.6	17.8	2.2	S	EC	Di	Silicified Diorite	fdsp, mafics	f	20							4	2	4		4																		tr	tr	tr					Lithology continues. Trace k-spar alt. associated with qtz veining. Hematite staining. 30 cm section of brecciated qtz, cabinate clay matrix with qtz clasts.					
L480738	17.8	19.8	2	S	EC	Di	Silicified Diorite	fdsp, mafics	v	20	v	50					3	3	4		3																			tr		1	tr					Lithology continues. Slight increase in epidote alt. cpy and py salvages on qtz veins.			
L480739	19.8	21.9	2.1	S	EC	Di	Silicified Diorite	fdsp, mafics	v	40	v	20					3	2	4		4																									Lithology continues.					
L480740	21.9	23.9	2	S	EC	Di	Silicified Diorite	fdsp, mafics	v	40	f	20					4	0	1		4																						1		tr	tr					Lithology continues. More silicified, darker rock, fine grained. Few qtz veins. Thin py vnlt. Increase in magnetite.
L480741	23.9	25.9	2	S	EC	Di	Silicified Diorite	fdsp, mafics	v	35							3	2	1		3																										Lithology continues. Still dark, finer grained diorite. Some leached calcite and sulphide veins. Blebs of cpy, moly salvages on qtz veins. Increase is qtz veining.				

L480763	64.4	66.7	2.3		S	KF	FD	pegmatic felsic dyke	fdsp, qtz, mafics	C	75									5	2	6			6			4	0	4	1	2	1	2		tr	tr	tr	tr	tr	FD lithology continues. End of sample is contact with Di at 70 dg. Hem staining on fractures. Chlorite veins.
L480764	66.7	68.6	1.9		S	EC	Di	Silicified Diorite	fdsp, hornblende, mafics	v	30	f	45							1	0	2			2			2	1	5	1	4	4	1		tr	tr	tr	tr	tr	Silicified Di. Most preserved original di texture so far, some chlorite veins. Some k-spar alt, and strong epidote alt along joint surfaces. Py in thin vnlts. Small cpy blebs.
L480765	Blank	CDN-BL-8																																							
L480766	68.6	70.6	2		S	EC	Di	Silicified Diorite	fdsp, hornblende, mafics	v	25	C	30							2	1	3			2			3	0	5	1	4	4	1		tr	tr	tr	tr	Lithology continues. 30 cm felsic dyke, C at 30 deg, fdsp alt to sericite. Xenoliths of country rock (10-30 cm).	
L480767	70.6	72.6	2		S	EC	Di	Silicified Diorite	fdsp, hornblende, mafics	f	40									3	1	4			3			2	0	5	1	3	4	1		tr	tr	tr	tr	Lithology continues. Moly as fracture coating. Sections of mtz supported breccia. Rock flour ltx, dark, clast mage from .2 to 3 cm. felsic clasts.	
L480768	72.6	74.8	2.2		S	EC	Di	Silicified Diorite	fdsp, hornblende, mafics	v	20	v	30							2	1	3			2			2	1	5	1	3	4	1		tr	tr	tr	tr	Lithology continues. Strong epidote and k-spar alt along joint surfaces. Small (5 cm) xenolith of country rock.	
L480769	74.8	76.7	1.9		S	EC	Di	Silicified Diorite	fdsp, hornblende, mafics	v	35									1	2	2			2			2	1	5	1	3	4	1		tr	tr	tr	tr	Lithology continues.	
L480770	76.7	78.7	2		S	EC	Di	Silicified Diorite	fdsp, hornblende, mafics	v	25									2	1	3			3			2	1	5	1	3	4	1		tr	tr	tr	tr	Lithology continues. Patches of Di texture.	
L480771	78.7	80.7	2		S	EC	Di	Silicified Diorite	fdsp, hornblende, mafics	v	40									1	1	3			2			2	1	5	1	3	4	1		tr	tr	tr	tr	lithology continues. Py as fracture coating. Decrease k-spar alt. small xenolith of country rock.	
L480772	80.7	82.8	2.1		S	EC	Di	Silicified Diorite	fdsp, hornblende, mafics	v	65	f	15							0	2	3			2			2	1	5	1	3	4	1		tr	tr	tr	tr	lithology continues. Di texture preserved. AR alt on fracture surfaces. Py as salvage on qtz/carb. Veins.	
L480773	82.8	84.8	2		S	EC	Di	Silicified Diorite	fdsp, hornblende, mafics	v	20	f	35							1	3	3			1			1	1	5	1	3	4	1		tr		1	tr	Lithology continues. Slight increase in py as disseminated, and qtz salvages. Magnetite confined to thin veins. Cpy vlt at 25 deg.	
L480774	84.8	86.3	1.5		S	EC	Di	Silicified Diorite	fdsp, hornblende, mafics	v	35									1	2	4			2			2	1	5	1	3	4	1		tr	tr	tr	tr	Lithology continues. Increase in k spar alt along joint surfaces. small Cpy blebs. Leached sulphide and carb veins.	
L480775	Standard	CDN-CM-11A																																							
L480776	86.3	87.8	1.5		S	EC	Di	Silicified Diorite	fdsp, hornblende, mafics	v	45	v	40							0	3	2			3			4	1	5	1	3	3	1		tr	tr	tr	tr	tr	Lithology continues. Continued increase in k-spar alt. py salvages.
L480777	87.8	89.9	2.1		S	AR/SQ	Di	Silicified Diorite	fdsp, hornblende, mafics	C	30	C	45	v	45					0	1	5			3			2	4	3	4	2	1	2		0	tr	tr	tr	Felsic dyle: AR alt. contact 30 deg uphole and 45 deg downhole. Fdsp alt. to clay and sericite, hornblende alt. to chlorite. 30 cm of fuscite, high Cr. 30 cm of bx, mtz sup. Clats 1-8mm.	
L480778	89.9	91.9	2		S	EC	Di	Silicified Diorite	fdsp, hornblende, mafics	v	25	v	50							1	2	3			4			2	0	5	1	3	3	2		0	tr	tr	tr	tr	Si Di lithology continues. High carbonate content in thin veins. K-spar and epidote alt along joint surfaces. Tr py in vnlts and on qtz vein as salvage.
L480779	91.9	94	2.1		S	EC	Di	Silicified Diorite	fdsp, hornblende, mafics	v	30	v	20							0	2	3			3			2	0	5	1	3	3	2		tr	tr	tr	tr	Lithology continues. Pegmatitic/ brecciated zone.	
L480780	94	96	2		S	KF	Di	Silicified Diorite	fdsp, hornblende, mafics	v	15					C	sa			0	3	2			1			4	0	5	1	2	2	1		tr	tr	tr	tr	Pegmatitic/ brecciated zone. Some clasts appear to be country rock. Variation from matrix to clast supported but mainly clst supported. Range from 1mm to 5 cm clasts. Felsic intrusive clsts. Cpy as salvages on qtz vein.	
L480781	96	98	2		S	EC	Di	Silicified Diorite	fdsp, hornblende, mafics	f	20	v	25							0	1	2			6			3	0	5	1	2	4	2		tr	tr	tr	tr	Silicified Di with mainly EC alt and some K-spar alt. high carbonate content. Clast supported bx in sections., xenolith of country rock. Tr py and cpy.	
L480782	98	100.1	2.1		S	EC	Di	Silicified Diorite	fdsp, hornblende, mafics	v	20	v	10							1	2	3			7			3	0	5	1	3	4	2		tr	tr	tr	tr	Lithology continues. 2 cm thick qtz veins with cpy salvages on edges (up to .5cm blebs)	
L480783	100.1	102.2	2.1		S	EC	Di	Silicified Diorite	fdsp, hornblende, mafics	v	80					C	sa			0	1	2			4			3	0	5	1	3	4	1		tr	tr	tr	tr	Lithology continues. Clst supported bx. (clasts country rock and felsic intrusive). Hematite staining. Increase in sulphides in brecciated section.	

L480784	102.2	104.7	2.5	S	EC	Di	Silicified Diorite	fdsp, hornblende, mafics	v	30	v	80	f	40	0	1	1	4	3	1	5	1	3	4	1			tr	tr	tr			Lithology continues. K-spar alt slightly decreases. 30 cm section of C sup. Bx. Sericite alt. on fractures.	
L480785	Blank	CDN-BL-8																																
L480786	104.7	106.7	2	S	EC	Di	Silicified Diorite	fdsp, hornblende, mafics	C	75	v	45			1	1	1	3	3	1	5	1	3	4	1			tr	tr	tr			Lithology continues. 30 cm thick section of pegmatic dyke, felsic, mafics alt. to chlorite. Contact at 75 downhole, gradational up hole with C sup bx. Magnetite drops out in dyke. Rest of sample is classic di. texture preserved.	
L480787	106.7	108.7	2	S	EC	Di	Silicified Diorite	fdsp, hornblende, mafics	v	40					2	2	3	2	2	1	5	1	4	4	1			tr	tr	tr			Lithology continues. Increase in chlorite veins. Qtz veins with py salvegs. Disseminated cpy. Thin Stingers of py	
L480788	108.7	110.8	2.1	S	EC	Di	Silicified Diorite	fdsp, hornblende, mafics, qtz	v	30					2	3	2	3	2	1	5	1	4	4	1			tr	tr	tr			Lithology continues. Some qtz grains in di. Calcite vein.	
L480789	110.8	112.8	2	S	EC	Di	Silicified Diorite	fdsp, hornblende, mafics	f	25	v	35	v	25	1	2	3	3	2	1	5	1	4	4	1			tr	tr	tr			Lithology continues. Hem. Staining on fracture surfaces. 40 cm of brecciation, clast sup, been mashed up, lots of carbonate veining, not much sulphides associated.	
L480790	112.8	114.1	1.3	S	KF	Di	felsic pegmatite dyke	fdsp, qtz, mafics	v	35					1	1	2	3	4	1	5	1	2	3	1			0	tr	tr			Pegmatitic dyke, felsic, completely alt. mafics, mainly alkali fdsp. Cpy salvegs on qtz vein. Contact gradational with breccia grading into dyke.	
L480791	114.1	115.4	1.3	S	EC	Di	Silicified Diorite	fdsp, hornblende, mafics, qtz	v	45	v	40			0	1	1	2	3	1	5	1	4	4	1			tr	tr	tr			Si Diorite. A few original qtz grains. 1 cm thick pegmatitic dyke. Strong epidote alt.	
L480792	115.4	117.4	2	S	EC	Di	Silicified Diorite	fdsp, hornblende, mafics, qtz	v	25	v	85			0	1	2	8	2	0	5	1	4	4	2			tr	tr	tr			Si Diorite with sections of bx with felsic and country rock clasts. Increase carbonate veining.	
L480793	117.4	119.4	2	S	EC	Di	Silicified Diorite	fdsp, hornblende, mafics, qtz	f	30	v	30			1	1	2	4	1	0	5	1	4	4	1			tr	tr	tr			Lithology continues. Decrease in K-spar alt. slight increase in grain size, still some qtz grains. Py salvegs along edges of qtz/carb veins.	
L480794	119.4	121.5	2.1	S	EC	Di	Silicified Diorite	fdsp, hornblende, mafics, qtz	v	5					0	2	3	6	1	0	5	1	4	4	2			tr	tr	tr			Lithology continues. Forst 60 cm of sample is di. Then grades into C sup breccia with country rock clsts and felsic intrusive clast. Clst size ranges fro .5 to 6 cm. evidence of deformation (undulating veins).	
L480795	121.5	123.7	2.2	S	EC	Di	Silicified Di/ Bx	fdsp, hornblende, mafics	v	55					2	3	1	5	1	1	5	1	4	4	2			tr	tr	tr			Lithology continues. Clst sup. Bx. with some large (10-20 cm) country rock clsts. Leached carbonate/Qtz/ and sulphide veins.	
L480796	123.7	125.4	1.7	S	AR	FD	felsic dyke	fdsp, mafics	v	40	v	75			2	3	3	4	1	4	3	4	2	1	2			tr	tr	tr			Di Lithology continues at begining of sample. 80 cm felsic dyke at 124.7 m. fuschite present, increase in mineralization (disseminated cpy and py) lots of qtz and carb veing, mafics alt. to chlorite. Possible siderite occurrence. Fdspd alt to clay and sericite.	
L480797	125.4	127.5	2.1	S	EC	Di	Silicified Di	fdsp, hornblende, mafics	v	55					1	2	2	2	1	0	5	1	4	4	2			tr	tr	tr			Silicified Di. Some country rock xenoliths. Strong epidote alt.	
L480798	127.5	129.5	2	S	EC	Di	Silicified Di	fdsp, hornblende, mafics	v	30					2	2	3	3	1	0	5	1	4	4	2			tr	tr	tr			Silicified Di. Country rock xenolith is fracture BX with epidote chlorite veins. Thin py vnlt. small cpy blebs.	
L480799	129.5	131.5	2	S	EC	Di	Silicified Di	fdsp, hornblende, mafics	v	35	v	45			3	4	3	2	1	0	5	1	3	4	2			tr		1	0.25			Silicified Di, large py blebs. Increase in mineralization cpy blebs up to .8 cm, occurring with epidote and k-spar alt along thick qtz vein.
L480800	131.5	133.5	2	S	EC	Di	Silicified Di	fdsp, hornblende, mafics	v	35	v	40			2	3	3	3	1	0	5	1	3	4	2			tr		1	0.25			Lithology continues. Few jasperoid veins. Large py blebs (2 cm).
L480801	133.5	135.5	2	S	EC	Di	Silicified Di	fdsp, hornblende, mafics	v	30					1	2	2	4	2	0	5	1	3	4	2			tr	tr	tr			Lithology continues. Two thin pegmatitic dykes. Country rock segments. Tr sulphides.	
L480802	135.5	137.8	2.3	S	KF	Di	felsic pegmatite dyke	fdsp, qtz, mafics	C	75					2	3	2	5	3	0	5	1	3	4	2			tr	tr	tr			Lithology continues. Pegmatitic dyke, large grains, felsic, monozite composition.	
L480803	137.8	138.9	1.1	S	KF	Di	felsic pegmatite dyke	fdsp, qtz, mafics							0	0	4	10	3	0	5	1	3	4	3			tr	tr	tr			Lithology continues. Pegmatitic dyke, large grains, felsic, monozite composition. Very alt. and mashed up, mayne carb. Veins.	

L480804	138.9	140.9	2		S	EC	Di	Silicified Di	fdsp, hornblende, mafics	v	20							1	1	2							2	0	5	1	4	4	2				tr	tr				Lithology continues. Mainly fined grained diorite. Finely disseminated py. Some country rock xenoliths.						
L480805	Blank	CDN-BL-8																																														
L480806	140.9	143	2.1		S	EC	Di	Silicified Di	fdsp, hornblende, mafics									0	0	1							1	0	5	1	4	4	1				tr	tr				Lithology continues. Smaller sections of bx, C sup. Not much veining or sulphides. Magnetite veins.						
L480807	143	145	2		S	EC	Di	Bx/ Silicified Di	fdsp, hornblende, mafics	v	70	v	25					C	sa									3	1	2			1	0	5	1	3	4	1			1	tr		enire smaple is clast sup. Bx. Sections of Mtx sup. .3 to 6 cm clsts. Felsic intrusive clsts, qtz vein fragments. Sed. Cists. Sulphides appear to increase with brecciation.			
L480808	145	147.1	2.1		S	EC	Di	Silicified Di	fdsp, hornblende, mafics	v	40	f	15						2	2	1							2	2	1			2			1	0	5	1	3	4	1			tr	tr	tr	Silicified Di. Original Di texture partially preserved, with sections of very EC alt.
L480809	147.1	149.1	2		S	EC	Di	Silicified Di	fdsp, hornblende, mafics	v	30								1	1	1							2	2	0	5	1	3	4	1				tr	tr				Lithology continues. Slight increase in K-spar alt.				
L480810	149.1	151.2	2.1		S	EC	Di	Silicified Di	fdsp, hornblende, mafics	v	15	v	20						1	0	2							3	0	5	1	3	4	1				tr	tr				Lithology continues. Still increasing in K-spar alt original di texture destroyed by EC alt.					
L480811	151.2	153.2	2		S	EC	Di	Silicified Di	fdsp, hornblende, mafics	v	20								4	2	2							2	0	5	1	3	4	1				1	tr	tr				Lithology continues. Pick up cpy in thin vnlt. Py also in vnlt and finely disseminated as well. Increase in magnetite.				
L480812	153.2	155.3	2.1		S	EC	Di	Silicified Di	fdsp, hornblende, mafics	v	25	F	30						4	3	3							2	2	1	5	1	3	2	1				1	tr	tr		tr		Lithology continues. Slight increase in K-spar alt. minor fault at 35 deg. Associated with 20 cm of shear rock with high clay content. Increased qtz veining with moly slaaves along edges and cubic pyrite.			
L480813	155.3	157.8	2.5		S	AR	FD	felsic dyke	fdsp, mafics	C	85	C	50						5	3	4							3	2	5	3	2	3	2				0			1	tr		tr		felsic dyke. Mainti AR alt with some sericitic alt. No magnetite. Increase in sulphides. Dimmeniated py and moly in qtz veins. Fuchs site occurrence. Contatc 85 deg up hole and 50 deg downhole.		
L480814	157.8	159.3	1.5		S	EC	Di	Silicified Di	fdsp, hornblende, mafics	C	70	C	40	v	45				1	1	2							3	0	5	1	3	4	1				tr	tr				tr		Silicified Di lithology continues. Small scale dyke, (20 cm) porphy texture, monzonite composition. fdsp Proporyblasts range from .2 -.4 cm in size. Rest of smaple is EC alt. tr amounts of visible moly in dyke.			
L480815	Standard	CDN-CM-11A																																														
L480816	159.3	160.9	1.6		S	EC	Di	Silicified Di	fdsp, hornblende, mafics	v	35								4	2	1							1	0	5	1	3	4	1				1			1				lithology continues. Multiple thin py vnlt and disseminated py. K-spar alt dmatically decreases.			
L480817	160.9	162.1	1.2		S	AR	FZ	Bx/fault zone	fdsp, mafics	v	85																													0			1		tr		entire sample is intensely affected by shear deformation (fault zone). Undualting veins, mtx supported brecciation. High clay content, high carbonate content. Very soft light rock. Dark qtz veins mixed with disseminated sulphides. Qtz vein frags. Have been roatated. mtrx of rock flour. broken core, unclear fault orientation.	
L480818	162.1	164.1	2		S	EC	Di	Silicified Di	fdsp, hornblende, mafics	v	70	v	85						1	2	3							2	1	5	1	4	4	3				tr	tr	tr				tr		silicified Di. Hematite staining. Strong chlorite and epidote. Tr cpy and py.		
L480819	164.1	166.1	2		S	EC	Di	Silicified Di	fdsp, hornblende, mafics	v	30	v	55						1	3	2							1	0	5	1	4	4	2				tr	tr	tr				tr		lithology continues. Cpy and py salvages on qtz veins.		
L480820	166.1	167.8	1.7		S	AR	FZ	Bx/fault zone	fdsp, mafics	F	15								1	2	6							1	3	5	4	2	1	3				0			tr	tr	tr			entire sample is intensely affected by shear deformation (fault zone). Undualting veins, mtx supported brecciation. High clay content, high carbonate content. Very soft light rock. Qtz vein frags. Have been roatated. mtrx of rock flour. broken core, fauly orientation of 15 deg. increased py close to fault surfaces.		
L480821	167.8	169.8	2		S	EC	Di	Silicified Di	fdsp, hornblende, mafics	v	20	v	40						2	1	2							2	0	5	1	4	4	1				tr	tr	tr				tr		silicified di. Tr sulphides. Two country rock xenoliths. Py vnlt.		

L480822	169.8	171.9	2.1		S	EC	Di	Silicified Di	fdsp, hornblende, mafics	v	40	v	85				1	0	1		1		1	0	5	1	4	3	1		tr	tr	tr		Lithology continues.
L480823	171.9	174	2.1		S	EC	Di	Silicified Di	fdsp, hornblende, mafics	v	35						2	0	1		1		3	0	5	1	3	4	1		tr	tr		lithology continues. More altered. Increased epidote and k-spar alt.	
L480824	174	175.7	1.7		S	EC	Di	Silicified Di	fdsp, hornblende, mafics	v	20						3	0	1		1		3	0	5	1	3	4	1		tr	tr		lithology continues. Thin py vnls.	
L480825	CDN-BL-8																																		
L480826	175.7	177.5	1.8		S	EC	Di	Silicified Di	fdsp, hornblende, mafics	v	60						2	0	2		1		3	0	5	1	3	4	1		tr	tr		tr	Lithology continues. Thin disseminated/qtz vnls in small section of C sup. Bx.
L480827	177.5	178.1	0.6		S	KF	FP	Felsic dyke	fdsp, qtz, mafics (bio)	C	75	v	20				1	0	0		2		4	1	5	0	2	1	1		0	tr		Felsic dyke: felsic porphyry. Qtz monozonite composition. relic bio, hornblende alt. to chlorite. Contact 75 deg up hole, downhole contact altered by epidote. Carbonate veins running through are later stage. Disseminated py throughout dyke.	
L480828	178.1	180.1	2		S	EC	Di	Silicified Di	fdsp, hornblende, mafics	C	70						1	0	1		2		2	0	5	1	4	4	1		tr	tr		Lithology continues. 3 small dykes (FP) crosscutting di at steep angles.	
L480829	180.1	181.2	1.1		S	EC	Di	Silicified Di	fdsp, hornblende, mafics	v	55						1	1	2		2		2	0	5	1	4	4	1		tr	tr		Lithology continues.	
L480830	181.2	182	0.8		S	KF	FP	Felsic dyke	fdsp, qtz, mafics (bio)	C	45						1	0	1		1		4	1	5	0	2	3	1		tr	tr		Felsic dyke: felsic porphyry. Qtz monozonite composition. relic bio, hornblende alt. to chlorite. Contact unclear up hole.	
L480831	182	183.3	1.3		S	EC	Di	Silicified Di	fdsp, hornblende, mafics	C	65	v	50				2	0	2		2		2	0	5	1	4	4	1		tr	tr		Silicified Di. One 15 cm dyke (FP). Thin py vnls, disseminated py in dyke.	
L480832	183.3	184.6	1.3		S	EC	Di	Silicified Di	fdsp, hornblende, mafics	V	65						2	0	1		2		2	0	5	1	4	4	1		tr	tr		lithology continues. 2 thinner felsic dykes, same comp., steep orientation to core axis.	
L480833	184.6	186.5	1.9		S	KF	FP	Felsic dyke	fdsp, mafics	v	70						0	0	0		1		4	1	5	1	2	2	1		0	tr		Felsic dyke: felsic porphyry. Qtz monozonite composition. relic bio, hornblende alt. to chlorite. Contact alt. uphole. Carbonate veins running through are later stage. Little py.	
L480834	186.5	188.1	1.6		S	KF	FP	Felsic dyke	fdsp, mafics	C	70	v	5				0	1	1		1		4	1	5	1	2	2	1		0	tr		dyke continues. downhole contact 70 deg downhole	
L480835	Standard	CDN-CGS-23																																	
L480836	188.1	190.1	2		S	EC	Di	Silicified Di	fdsp, hornblende, mafics	f	25	v	20				1	0	1		3		2	0	5	1	4	4	1		tr	tr		silicified di, some sections of C sup bx. Di, FP, and country rock clsts. Strong epidote alt. throughout.	
L480837	190.1	192.1	2		S	EC	Di	Silicified Di	fdsp, hornblende, mafics	f	40	v	25				0	1	2		4		3	0	5	1	4	4	1		tr	tr		lithology continues. More altered. Original texture texture destroyed.	
L480838	192.1	194.1	2		S	EC	Di	Silicified Di	fdsp, hornblende, mafics	f	50						1	1	3		3		2	0	5	1	4	4	2		tr	tr		lithology continues. Decrease in K-spar alt.	
L480839	194.1	196.2	2.1		S	EC	Di	Silicified Di	fdsp, hornblende, mafics	v	30						0	0	1		2		2	0	5	1	4	4	3		tr	tr		lithology continues. High carbonate content. Sections of mtx sup. Bx. Country rock clsts, felsic intrusive clst.	
L480840	196.2	198.4	2.2		S	EC	Di	Silicified Di	fdsp, hornblende, mafics	f	40	v	45				1	1	2		3		2	0	5	1	4	4	2		tr	tr		Lithology continues. Sections of mtx sup. Bx. Py salvages on qtz/carb vein.	
L480841	198.4	200.6	2.2		S	EC	Di	Silicified Di	fdsp, hornblende, mafics	f	10	f	20				0	1	2		2		1	0	5	1	4	4	1		tr	tr		Lithology continues. Py salvages on qtz/carb veins. K-spar alt. on joint surfaces.	
L480842	200.6	201.4	0.8		S	KF	FP	Felsic dyke	fdsp, mafics	C	65						1	0	0		2		4	1	5	1	2	2	1		tr	0.5		Felsic dyke: felsic porphyry. Qtz monozonite composition. relic bio, hornblende alt. to chlorite. Contact at 65 deg., disseminated py throughout. KF alt.	

L480862	230	232	2	S	EC	Di	Silicified Di	fdsp, hornblende, mafics	v	60							1	0	1		1															tr	tr	0.25				lithology continues. Cpy in country rock. K-spar alt. along joint surfaces, strong epidote alt.
L480863	232	234.4	2.4	S	EC	Di	Silicified Di	fdsp, hornblende, mafics	v	25							1	0	2		2															tr	tr	0.25				Lithology continues.
L480864	234.4	236.8	2.4	S	EC	Di	Silicified Di	fdsp, hornblende, mafics	C	70	C	65					2	0	1		1															tr	tr	tr				Lithology continues. 2 small scale felsic dykes. Contact at 70 65 deg. FP, Mz comp. KF alt. margins of dyke associated with brecciations and increased epidote alt.
L480865	Blank	CDN-BL-8																																								
L480866	EOH																																									

Appendix E: Analytical Certificates



ALS Canada Ltd.
2103 Dollarton Hwy
North Vancouver BC V7H 0A7
Téléphone: 604 984 0221 Télécopieur: 604 984 0218
www.alsglobal.com

À: PAGET MINERALS CORPORATION
1160 - 1040 W. GEORGIA ST.
VANCOUVER BC V6E 4H1

Page: 1
Finalisée date: 7-AOUT-2011
Cette copie a fait un rapport sur
9-NOV-2011
Compte: PAGMIN

CERTIFICAT TR11133620

Projet: Icy Lake

Bon de commande #:

Ce rapport s'applique aux 36 échantillons de carotte forage soumis à notre laboratoire de Terrace, BC, Canada le 14-JUIL-2011.

Les résultats sont transmis à:

SONIA JEYACHANDRAN

ROD OGILVIE

DAVID VOLKERT

PRÉPARATION ÉCHANTILLONS

CODE ALS	DESCRIPTION
WEI-21	Poids échantillon reçu
LOG-22	Entrée échantillon - Reçu sans code barre
CRU-QC	Test concassage QC
PUL-QC	Test concassage QC
CRU-31	Granulation - 70 % <2 mm
SPL-21	Échant. fractionné - div. riffles
PUL-31	Pulvérisé à 85 % <75 um
LOG-23	Entrée pulpe - Reçu avec code barre

PROCÉDURES ANALYTIQUES

CODE ALS	DESCRIPTION	INSTRUMENT
Au-ICP21	Au 30 g FA fini ICP-AES	ICP-AES
ME-ICP41	Aqua regia ICP-AES 35 éléments	ICP-AES

À: PAGET MINERALS CORPORATION
ATTN: DAVID VOLKERT
1160 - 1040 W. GEORGIA ST.
VANCOUVER BC V6E 4H1

Ce rapport est final et remplace tout autre rapport préliminaire portant ce numéro de certificat. Les résultats s'appliquent aux échantillons soumis. Toutes les pages de ce rapport ont été vérifiées et approuvées avant publication.

Signature:



Colin Ramshaw, Vancouver Laboratory Manager



ALS Canada Ltd.

2103 Dollarton Hwy
North Vancouver BC V7H 0A7
Téléphone: 604 984 0221 Télécopieur: 604 984 0218
www.alsglobal.com

À: PAGET MINERALS CORPORATION
1160 - 1040 W. GEORGIA ST.
VANCOUVER BC V6E 4H1

Page: 2 - A
Nombre total de pages: 2 (A -
C)
Finalisée date: 7-AOUT-2011
Compte: PAGMIN

Projet: Icy Lake

CERTIFICAT D'ANALYSE TR11133620

Description échantillon	Méthode élément unités L.D.	WEI-21	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41
		Poids reçu kg	Ag ppm	Al %	As ppm	B ppm	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	Ga ppm
L480523		7.97	0.2	0.82	5	<10	50	<0.5	2	0.69	<0.5	12	17	249	2.13	<10
L480524		9.84	0.3	1.07	5	<10	50	<0.5	2	1.02	<0.5	15	21	432	3.02	10
L480525		0.07	0.2	0.98	4	<10	70	<0.5	<2	0.61	<0.5	6	29	21	1.86	<10
L480526		9.14	0.6	0.99	7	<10	50	<0.5	6	0.94	<0.5	18	18	526	2.94	10
L480527		8.90	0.5	1.01	6	<10	60	<0.5	3	0.93	<0.5	13	18	409	2.99	10
L480528		9.30	0.4	1.07	6	<10	50	<0.5	2	1.11	<0.5	15	26	430	2.87	10
L480529		9.38	0.6	1.21	5	<10	60	<0.5	8	1.19	<0.5	16	19	663	2.93	10
L480530		8.92	0.5	2.20	5	<10	80	<0.5	5	1.01	<0.5	15	64	367	3.42	10
L480531		7.94	0.2	0.81	6	<10	60	<0.5	<2	0.73	<0.5	9	17	218	2.11	<10
L480532		7.51	0.2	0.88	4	<10	60	<0.5	<2	0.66	<0.5	7	18	308	1.63	<10
L480533		9.59	0.2	0.82	4	<10	70	<0.5	<2	0.67	<0.5	6	20	221	1.49	<10
L480534		8.49	0.3	0.91	4	<10	50	<0.5	<2	0.63	<0.5	5	20	264	1.43	<10
L480535		0.07	1.7	1.19	14	<10	120	<0.5	2	0.64	<0.5	7	29	3350	2.97	<10
L480536		7.88	0.9	1.10	4	<10	60	<0.5	<2	1.11	<0.5	11	16	994	2.01	<10
L480537		3.87	1.0	0.84	5	<10	50	<0.5	2	1.18	<0.5	12	18	1080	2.23	<10
L480538		4.48	0.7	0.96	5	<10	60	<0.5	<2	1.25	<0.5	11	19	758	1.95	<10
L480539		4.83	1.5	0.83	6	<10	50	<0.5	2	1.13	<0.5	14	22	1650	1.97	<10
L480540		4.33	2.0	1.18	7	<10	60	<0.5	10	1.46	<0.5	23	6	2230	2.17	10
L480541		4.87	0.9	0.90	27	<10	50	<0.5	5	2.04	<0.5	191	19	501	6.88	<10
L480542		4.64	1.0	1.13	193	<10	140	0.6	2	5.13	<0.5	22	13	651	2.59	<10
L480543		4.44	0.4	0.71	17	<10	490	<0.5	<2	2.08	<0.5	9	11	408	1.93	<10
L480544		4.45	0.8	0.57	32	<10	30	<0.5	15	2.69	<0.5	66	5	376	4.82	<10
L480545		0.07	0.3	0.98	8	<10	80	<0.5	<2	0.64	<0.5	6	30	21	1.95	<10
L480546		4.68	0.5	0.64	7	<10	70	<0.5	<2	1.13	<0.5	13	10	504	2.03	<10
L480547		4.99	0.6	0.74	5	<10	60	<0.5	<2	1.15	<0.5	13	11	613	2.19	<10
L480548		4.55	0.6	0.56	7	<10	50	<0.5	2	1.16	<0.5	11	9	649	1.53	<10
L480549		4.55	0.3	0.54	5	<10	50	<0.5	2	1.15	<0.5	13	10	427	1.69	<10
L480550		4.96	0.5	0.67	7	<10	40	<0.5	<2	1.17	<0.5	18	11	589	1.84	<10
L480551		4.72	0.4	0.66	8	<10	30	<0.5	2	1.11	<0.5	26	10	585	1.89	<10
L480552		4.79	0.3	0.76	16	<10	40	<0.5	2	1.02	<0.5	76	23	394	2.56	<10
L480553		4.80	0.2	0.89	11	<10	50	<0.5	<2	1.08	<0.5	16	19	387	1.44	<10
L480554		4.39	0.3	0.82	13	<10	60	<0.5	<2	1.08	<0.5	38	21	751	1.62	<10
L480555		0.07	2.0	1.48	30	<10	230	<0.5	2	1.82	0.8	16	62	1885	4.10	<10
L480556		4.50	0.4	0.63	3	<10	40	<0.5	<2	1.10	<0.5	13	18	631	1.28	<10
L480557		5.00	0.3	0.79	2	<10	130	<0.5	<2	1.50	<0.5	8	24	564	1.74	<10
L480558		2.99	<0.2	0.71	3	<10	80	<0.5	<2	0.73	<0.5	5	24	266	1.16	<10



ALS Canada Ltd.
 2103 Dollarton Hwy
 North Vancouver BC V7H 0A7
 Téléphone: 604 984 0221 Télécopieur: 604 984 0218
 www.alsglobal.com

À: PAGET MINERALS CORPORATION
 1160 - 1040 W. GEORGIA ST.
 VANCOUVER BC V6E 4H1

Page: 2 - B
 Nombre total de pages: 2 (A - C)
 Finalisée date: 7-AOUT-2011
 Compte: PAGMIN

Projet: Icy Lake

CERTIFICAT D'ANALYSE TR11133620

Description échantillon	Méthode élément unités L.D.	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	
		Hg	K	La	Mg	Mn	Mo	Na	Ni	P	Pb	S	Sb	Sc	Sr	Th
		ppm	%	ppm	%	ppm	ppm	%	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm
		1	0.01	10	0.01	5	1	0.01	1	10	2	0.01	2	1	1	20
L480523		<1	0.28	<10	0.54	124	150	0.08	9	1090	3	0.69	<2	3	43	<20
L480524		<1	0.33	<10	0.62	134	312	0.09	13	1100	3	1.26	<2	3	70	<20
L480525		<1	0.06	<10	0.44	292	4	0.05	20	470	2	0.05	<2	4	29	<20
L480526		<1	0.46	<10	0.82	147	224	0.09	13	1280	5	1.61	<2	3	40	<20
L480527		<1	0.38	<10	0.65	152	117	0.09	10	1310	<2	0.99	<2	3	59	<20
L480528		<1	0.32	<10	0.61	141	205	0.09	13	1270	2	0.97	<2	3	59	<20
L480529		<1	0.31	<10	0.68	135	132	0.09	13	1340	2	1.05	<2	4	52	<20
L480530		<1	1.30	<10	2.35	282	479	0.10	19	1320	5	1.82	<2	11	44	<20
L480531		<1	0.28	<10	0.53	98	361	0.09	9	650	5	1.41	<2	2	33	<20
L480532		<1	0.33	<10	0.53	107	316	0.09	8	550	2	0.50	<2	3	35	<20
L480533		<1	0.29	<10	0.53	102	291	0.07	8	550	2	0.48	<2	3	52	<20
L480534		<1	0.35	<10	0.53	98	530	0.09	7	570	2	0.40	<2	3	33	<20
L480535		<1	0.10	<10	0.52	408	249	0.08	28	500	21	0.41	4	4	37	<20
L480536		<1	0.31	<10	0.56	113	411	0.10	10	1270	<2	0.64	<2	4	70	<20
L480537		<1	0.19	<10	0.55	148	505	0.08	9	1330	9	0.73	<2	3	45	<20
L480538		<1	0.22	<10	0.54	134	369	0.09	11	1240	4	0.73	<2	2	52	<20
L480539		<1	0.19	<10	0.51	128	394	0.10	16	910	7	0.90	<2	2	56	<20
L480540		<1	0.29	<10	0.68	119	760	0.10	8	1330	6	1.21	<2	4	58	<20
L480541		<1	0.57	<10	0.93	170	164	0.05	22	1020	10	8.18	2	6	35	<20
L480542		<1	0.26	<10	0.80	272	749	0.03	19	890	7	1.54	7	8	125	<20
L480543		<1	0.21	<10	0.53	182	489	0.07	5	790	3	0.66	<2	4	116	<20
L480544		<1	0.22	<10	0.54	181	252	0.04	10	1080	12	4.84	<2	5	68	<20
L480545		<1	0.06	<10	0.46	303	4	0.05	20	480	2	0.06	<2	4	29	<20
L480546		<1	0.16	<10	0.58	119	926	0.09	7	1240	7	1.01	<2	3	39	<20
L480547		<1	0.18	10	0.48	137	351	0.09	6	1370	3	0.75	<2	2	40	<20
L480548		<1	0.16	<10	0.34	110	1330	0.09	7	1240	6	0.72	<2	2	34	<20
L480549		<1	0.13	<10	0.30	99	405	0.09	7	1190	5	0.81	<2	2	37	<20
L480550		<1	0.15	<10	0.32	94	313	0.10	8	1210	2	1.02	<2	2	43	<20
L480551		<1	0.15	<10	0.42	97	828	0.08	10	1100	4	1.16	<2	2	38	<20
L480552		<1	0.17	<10	0.40	100	426	0.10	27	1010	5	1.62	<2	2	49	<20
L480553		<1	0.18	<10	0.36	81	470	0.12	15	1010	7	0.75	<2	2	78	<20
L480554		<1	0.20	<10	0.41	109	945	0.13	16	650	8	0.86	<2	2	41	<20
L480555		1	0.49	20	0.82	352	153	0.06	16	710	22	1.91	8	6	74	<20
L480556		<1	0.13	<10	0.33	93	234	0.10	10	680	6	0.47	<2	2	39	<20
L480557		<1	0.16	<10	0.50	140	684	0.08	12	630	4	0.49	<2	2	49	<20
L480558		<1	0.18	<10	0.48	108	351	0.10	9	440	4	0.23	<2	2	37	<20



ALS Canada Ltd.
 2103 Dollarton Hwy
 North Vancouver BC V7H 0A7
 Téléphone: 604 984 0221 Télécopieur: 604 984 0218
 www.alsglobal.com

À: PAGET MINERALS CORPORATION
 1160 - 1040 W. GEORGIA ST.
 VANCOUVER BC V6E 4H1

Page: 2 - C
 Nombre total de pages: 2 (A - C)
 Finalisée date: 7-AOUT-2011
 Compte: PAGMIN

Projet: Icy Lake

CERTIFICAT D'ANALYSE TR11133620

Description échantillon	Méthode élément unités L.D.	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	Au-ICP21
		Ti %	Ti ppm	U ppm	V ppm	W ppm	Zn ppm	Au ppm
		0.01	10	10	1	10	2	0.001
L480523		0.16	<10	<10	72	50	32	0.015
L480524		0.20	<10	<10	102	130	19	0.033
L480525		0.10	<10	<10	43	10	33	0.002
L480526		0.25	<10	<10	116	40	25	0.037
L480527		0.20	<10	<10	100	120	18	0.021
L480528		0.20	<10	<10	103	30	18	0.016
L480529		0.20	<10	<10	107	20	21	0.017
L480530		0.24	<10	<10	135	30	43	0.024
L480531		0.13	<10	<10	48	20	15	0.015
L480532		0.13	<10	<10	53	20	14	0.005
L480533		0.12	<10	<10	51	30	12	0.010
L480534		0.12	<10	<10	56	10	12	0.009
L480535		0.11	<10	<10	49	<10	50	1.025
L480536		0.17	<10	<10	81	30	18	0.040
L480537		0.16	<10	<10	81	10	20	0.016
L480538		0.17	<10	<10	74	40	15	0.016
L480539		0.17	<10	<10	65	20	18	0.028
L480540		0.21	<10	<10	91	20	25	0.071
L480541		0.08	<10	<10	70	<10	32	0.035
L480542		<0.01	<10	<10	49	<10	34	0.027
L480543		0.03	<10	<10	43	10	14	0.011
L480544		0.01	<10	<10	29	90	19	0.215
L480545		0.10	<10	<10	44	10	34	0.002
L480546		0.15	<10	<10	53	10	16	0.014
L480547		0.18	<10	<10	66	20	17	0.019
L480548		0.17	<10	<10	48	30	17	0.039
L480549		0.16	<10	<10	48	20	12	0.019
L480550		0.16	<10	<10	49	30	11	0.018
L480551		0.14	<10	<10	51	40	15	0.032
L480552		0.15	<10	<10	53	10	17	0.020
L480553		0.13	<10	<10	43	20	14	0.021
L480554		0.11	<10	<10	40	10	22	0.017
L480555		0.04	<10	<10	56	<10	67	0.203
L480556		0.10	<10	<10	40	10	15	0.018
L480557		0.08	<10	<10	45	20	17	0.030
L480558		0.10	<10	<10	42	10	13	0.006



ALS Canada Ltd.
2103 Dollarton Hwy
North Vancouver BC V7H 0A7
Téléphone: 604 984 0221 Télécopieur: 604 984 0218
www.alsglobal.com

À: PAGET MINERALS CORPORATION
1160 - 1040 W. GEORGIA ST.
VANCOUVER BC V6E 4H1

Page: 1
Finalisée date:
13-AOUT-2011
Cette copie a fait un rapport sur
9-NOV-2011
Compte: PAGMIN

CERTIFICAT TR11138182

Projet: Icy Lake

Bon de commande #:

Ce rapport s'applique aux 172 échantillons de carotte forage soumis à notre laboratoire de Terrace, BC, Canada le 21-JUIL-2011.

Les résultats sont transmis à:

SONIA JEYACHANDRAN

ROD OGILVIE

DAVID VOLKERT

PRÉPARATION ÉCHANTILLONS

CODE ALS	DESCRIPTION
WEI-21	Poids échantillon reçu
LOG-22	Entrée échantillon - Reçu sans code barre
CRU-QC	Test concassage QC
PUL-QC	Test concassage QC
CRU-31	Granulation - 70 % <2 mm
SPL-21	Échant. fractionné - div. riffles
PUL-31	Pulvérisé à 85 % <75 um
LOG-23	Entrée pulpe - Reçu avec code barre

PROCÉDURES ANALYTIQUES

CODE ALS	DESCRIPTION	INSTRUMENT
Au-ICP21	Au 30 g FA fini ICP-AES	ICP-AES
ME-ICP41	Aqua regia ICP-AES 35 éléments	ICP-AES

À: PAGET MINERALS CORPORATION
ATTN: DAVID VOLKERT
1160 - 1040 W. GEORGIA ST.
VANCOUVER BC V6E 4H1

Ce rapport est final et remplace tout autre rapport préliminaire portant ce numéro de certificat. Les résultats s'appliquent aux échantillons soumis. Toutes les pages de ce rapport ont été vérifiées et approuvées avant publication.

Signature:



Colin Ramshaw, Vancouver Laboratory Manager



ALS Canada Ltd.

2103 Dollarton Hwy
North Vancouver BC V7H 0A7
Téléphone: 604 984 0221 Télécopieur: 604 984 0218
www.alsglobal.com

À: PAGET MINERALS CORPORATION
1160 - 1040 W. GEORGIA ST.
VANCOUVER BC V6E 4H1

Page: 2 - A
Nombre total de pages: 6 (A - C)

Finalisée date:
13-AOUT-2011
Compte: PAGMIN

Projet: Icy Lake

CERTIFICAT D'ANALYSE TR11138182

Description échantillon	Méthode élément unités L.D.	WEI-21	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	
		Poids reçu kg	Ag ppm	Al %	As ppm	B ppm	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	Ga ppm
		0.02	0.2	0.01	2	10	10	0.5	2	0.01	0.5	1	1	1	0.01	10
L480559		3.38	0.2	0.56	16	<10	50	<0.5	<2	0.58	<0.5	4	22	196	0.98	<10
L480560		4.39	0.8	0.66	6	<10	50	<0.5	<2	0.94	<0.5	6	23	810	1.31	<10
L480561		4.54	0.3	0.77	10	<10	30	<0.5	3	1.19	<0.5	8	26	279	1.64	<10
L480562		5.08	<0.2	0.84	4	<10	30	<0.5	<2	1.21	<0.5	7	30	163	2.07	<10
L480563		5.04	<0.2	0.93	6	<10	20	<0.5	2	1.32	<0.5	7	38	130	2.08	10
L480564		4.79	0.4	0.92	3	<10	40	<0.5	<2	1.21	<0.5	8	28	551	1.77	<10
L480565		0.08	0.5	1.03	4	<10	80	<0.5	<2	0.63	<0.5	8	29	20	2.00	<10
L480566		4.88	0.7	0.88	8	<10	40	<0.5	4	2.08	<0.5	39	42	446	2.22	<10
L480567		4.40	0.8	0.99	12	<10	50	<0.5	<2	1.87	<0.5	50	41	859	2.10	<10
L480568		4.49	0.8	0.74	9	<10	40	<0.5	<2	1.08	<0.5	21	31	826	1.72	<10
L480569		4.71	0.4	0.74	5	<10	30	<0.5	5	1.02	<0.5	14	37	460	1.58	<10
L480570		4.84	0.3	0.92	2	<10	50	<0.5	<2	1.22	<0.5	9	43	416	1.98	<10
L480571		4.59	0.3	0.73	3	<10	60	<0.5	2	1.02	<0.5	6	23	349	1.57	<10
L480572		4.63	0.5	0.78	4	<10	40	<0.5	3	1.04	<0.5	9	32	618	1.74	<10
L480573		4.88	1.0	1.49	3	<10	40	<0.5	<2	1.40	<0.5	12	56	809	2.12	<10
L480574		4.80	0.3	1.10	5	<10	40	<0.5	2	1.14	<0.5	13	34	490	1.81	<10
L480575		0.08	3.6	1.74	33	<10	130	<0.5	4	1.00	1.1	19	57	8940	4.51	10
L480576		4.52	0.4	1.32	3	<10	50	<0.5	5	1.12	<0.5	8	32	421	1.84	<10
L480577		5.38	0.7	0.88	4	<10	40	<0.5	2	1.17	<0.5	10	19	606	1.90	<10
L480578		4.28	0.4	0.71	3	<10	30	<0.5	4	0.97	<0.5	9	10	360	1.78	<10
L480579		4.91	0.6	0.53	3	<10	40	<0.5	4	0.86	<0.5	7	8	613	1.26	<10
L480580		4.91	0.6	0.65	4	<10	30	<0.5	5	1.08	<0.5	10	18	655	1.86	<10
L480581		4.86	0.6	0.84	6	<10	40	<0.5	<2	1.35	<0.5	9	21	424	1.84	<10
L480582		4.97	0.3	0.72	4	<10	40	<0.5	<2	1.09	<0.5	10	19	422	1.80	<10
L480583		4.56	0.3	0.71	3	<10	50	<0.5	2	0.94	<0.5	7	18	250	1.61	<10
L480584		4.83	0.5	0.42	2	<10	50	<0.5	<2	0.84	<0.5	6	11	481	0.96	<10
L480585		0.08	0.2	1.05	5	<10	80	<0.5	<2	0.64	<0.5	7	29	20	2.00	<10
L480586		4.74	0.3	0.77	4	<10	50	<0.5	<2	1.09	<0.5	8	18	562	1.62	<10
L480587		4.32	<0.2	1.16	3	<10	50	<0.5	2	1.91	<0.5	7	23	117	2.41	10
L480588		5.28	0.9	0.75	5	<10	50	<0.5	<2	1.08	<0.5	7	20	440	2.25	<10
L480589		4.53	0.4	0.57	4	<10	40	<0.5	4	0.86	<0.5	14	17	529	1.55	<10
L480590		4.94	2.8	1.42	99	<10	40	<0.5	8	0.79	<0.5	180	19	3390	9.53	10
L480591		4.99	0.5	0.53	4	<10	40	<0.5	2	0.99	<0.5	14	10	437	1.64	<10
L480592		5.14	0.2	0.59	3	<10	30	<0.5	<2	0.83	<0.5	7	11	296	1.74	<10
L480593		4.77	0.6	0.57	3	<10	30	<0.5	4	1.00	<0.5	6	12	903	1.01	<10
L480594		4.95	0.7	0.52	3	<10	30	<0.5	2	0.97	<0.5	7	12	890	1.28	<10
L480595		0.08	3.6	1.78	35	<10	130	<0.5	9	1.00	1.0	18	57	9170	4.49	<10
L480596		4.76	0.5	0.46	4	<10	30	<0.5	33	0.80	<0.5	16	12	594	1.63	<10
L480597		4.93	0.7	0.86	5	<10	140	<0.5	4	1.85	<0.5	11	45	481	2.26	<10
L480598		4.53	0.5	0.53	<2	<10	40	<0.5	2	1.20	<0.5	7	12	682	0.97	<10



ALS Canada Ltd.
 2103 Dollarton Hwy
 North Vancouver BC V7H 0A7
 Téléphone: 604 984 0221 Télécopieur: 604 984 0218
 www.alsglobal.com

À: PAGET MINERALS CORPORATION
 1160 - 1040 W. GEORGIA ST.
 VANCOUVER BC V6E 4H1

Page: 2 - B
 Nombre total de pages: 6 (A - C)

Finalisée date:
 13-AOUT-2011
 Compte: PAGMIN

Projet: Icy Lake

CERTIFICAT D'ANALYSE TR11138182

Description échantillon	Méthode élément unités L.D.	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	
		Hg ppm 1	K % 0.01	La ppm 10	Mg % 0.01	Mn ppm 5	Mo ppm 1	Na % 0.01	Ni ppm 1	P ppm 10	Pb ppm 2	S % 0.01	Sb ppm 2	Sc ppm 1	Sr ppm 1	Th ppm 20
L480559		<1	0.13	10	0.30	90	322	0.08	6	280	5	0.17	<2	1	27	<20
L480560		<1	0.15	<10	0.28	94	714	0.08	9	730	4	0.33	<2	1	45	<20
L480561		<1	0.12	<10	0.43	136	616	0.09	11	760	3	0.38	<2	2	51	<20
L480562		<1	0.10	<10	0.46	156	415	0.10	10	880	2	0.25	<2	2	67	<20
L480563		<1	0.13	<10	0.61	180	794	0.10	12	910	3	0.20	<2	3	52	<20
L480564		<1	0.18	<10	0.58	144	742	0.10	12	930	2	0.32	2	2	58	<20
L480565		<1	0.06	<10	0.47	302	4	0.05	18	480	<2	0.05	<2	4	29	<20
L480566		<1	0.15	10	0.91	230	884	0.10	27	820	5	1.08	<2	5	47	<20
L480567		<1	0.28	10	0.84	222	450	0.09	21	900	4	0.78	<2	4	41	<20
L480568		<1	0.14	<10	0.53	120	1400	0.09	20	790	3	0.94	<2	2	33	<20
L480569		<1	0.14	<10	0.63	127	536	0.09	20	800	3	0.61	<2	2	30	<20
L480570		<1	0.14	<10	0.50	148	72	0.10	16	910	<2	0.36	<2	3	48	<20
L480571		<1	0.12	<10	0.25	93	290	0.10	7	860	2	0.37	<2	1	68	<20
L480572		<1	0.11	<10	0.25	92	177	0.10	11	880	2	0.39	<2	1	111	<20
L480573		<1	0.22	<10	0.54	143	589	0.19	25	970	2	0.44	<2	3	210	<20
L480574		<1	0.19	<10	0.37	116	106	0.15	11	890	<2	0.41	<2	2	88	<20
L480575		<1	0.52	10	1.02	513	908	0.11	32	870	38	2.12	6	9	49	<20
L480576		<1	0.26	<10	0.51	128	928	0.17	8	800	2	0.34	<2	3	87	<20
L480577		<1	0.13	<10	0.37	105	201	0.10	7	840	2	0.58	<2	2	78	<20
L480578		<1	0.12	<10	0.22	82	512	0.10	4	810	2	0.82	<2	1	73	<20
L480579		<1	0.11	<10	0.15	73	461	0.09	3	740	2	0.50	<2	1	68	<20
L480580		<1	0.10	<10	0.26	105	374	0.10	8	970	2	0.66	<2	2	56	<20
L480581		<1	0.13	10	0.35	114	397	0.10	8	910	2	0.50	<2	2	61	<20
L480582		<1	0.10	10	0.30	101	186	0.10	7	810	<2	0.36	<2	2	62	<20
L480583		<1	0.11	<10	0.25	89	252	0.09	4	720	2	0.27	<2	1	58	<20
L480584		<1	0.10	<10	0.17	71	3590	0.07	3	610	2	0.48	<2	1	40	<20
L480585		<1	0.06	<10	0.47	302	9	0.06	18	480	<2	0.05	<2	4	30	<20
L480586		<1	0.14	<10	0.34	98	340	0.11	6	790	<2	0.36	<2	2	67	<20
L480587		<1	0.13	10	0.89	202	102	0.12	9	830	<2	0.20	<2	5	58	<20
L480588		<1	0.10	10	0.47	155	137	0.12	7	830	2	0.22	2	2	56	<20
L480589		<1	0.14	<10	0.29	87	637	0.09	6	730	3	0.48	<2	1	58	<20
L480590		<1	0.11	<10	0.53	133	258	0.07	28	720	10	6.20	3	3	37	<20
L480591		<1	0.09	10	0.14	70	1090	0.09	3	870	3	0.66	<2	1	79	<20
L480592		<1	0.10	<10	0.18	66	274	0.09	7	820	6	0.46	<2	1	56	<20
L480593		<1	0.14	<10	0.17	67	1200	0.08	5	810	3	0.44	<2	1	47	<20
L480594		<1	0.11	10	0.12	55	378	0.08	4	880	2	0.45	<2	1	55	<20
L480595		<1	0.53	10	1.02	512	916	0.12	33	870	35	2.16	6	9	51	<20
L480596		<1	0.11	<10	0.16	58	429	0.08	5	740	3	1.04	<2	1	35	<20
L480597		<1	0.17	10	0.59	160	629	0.07	16	840	3	1.02	<2	2	38	<20
L480598		<1	0.14	<10	0.47	91	203	0.06	7	750	2	0.32	<2	2	25	<20



ALS Canada Ltd.
 2103 Dollarton Hwy
 North Vancouver BC V7H 0A7
 Téléphone: 604 984 0221 Télécopieur: 604 984 0218
 www.alsglobal.com

À: PAGET MINERALS CORPORATION
 1160 - 1040 W. GEORGIA ST.
 VANCOUVER BC V6E 4H1

Page: 2 - C
 Nombre total de pages: 6 (A - C)

Finalisée date:
 13-AOUT-2011
 Compte: PAGMIN

Projet: Icy Lake

CERTIFICAT D'ANALYSE TR11138182

Description échantillon	Méthode élément unités L.D.	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	Au-ICP21
		Ti %	Ti ppm	U ppm	V ppm	W ppm	Zn ppm	Au ppm
		0.01	10	10	1	10	2	0.001
L480559		0.07	<10	<10	28	10	14	0.005
L480560		0.13	<10	<10	43	10	18	0.014
L480561		0.14	<10	<10	52	20	14	0.007
L480562		0.15	<10	<10	68	20	15	0.003
L480563		0.16	<10	<10	70	40	16	0.002
L480564		0.18	<10	<10	66	70	19	0.012
L480565		0.10	<10	<10	44	10	33	0.001
L480566		0.12	<10	<10	70	<10	22	0.025
L480567		0.15	<10	<10	70	30	24	0.024
L480568		0.14	<10	<10	52	10	18	0.055
L480569		0.15	<10	<10	56	10	19	0.028
L480570		0.16	<10	<10	69	20	14	0.008
L480571		0.13	<10	<10	50	70	11	0.008
L480572		0.14	<10	<10	59	30	11	0.006
L480573		0.15	<10	<10	74	80	22	0.016
L480574		0.15	<10	<10	61	80	14	0.008
L480575		0.15	<10	<10	100	20	151	0.693
L480576		0.17	<10	<10	68	20	15	0.013
L480577		0.14	<10	<10	57	20	17	0.008
L480578		0.13	<10	<10	42	20	11	0.008
L480579		0.11	<10	<10	32	30	12	0.014
L480580		0.16	<10	<10	54	20	14	0.019
L480581		0.14	<10	<10	58	40	15	0.003
L480582		0.14	<10	<10	57	20	14	0.016
L480583		0.12	<10	<10	48	20	9	0.004
L480584		0.09	<10	<10	28	20	9	0.007
L480585		0.11	<10	<10	45	10	32	0.001
L480586		0.13	<10	<10	52	10	12	0.011
L480587		0.10	<10	<10	78	10	16	0.002
L480588		0.15	<10	<10	72	10	21	0.004
L480589		0.15	<10	<10	49	20	11	0.012
L480590		0.11	<10	<10	49	20	39	0.087
L480591		0.13	<10	<10	44	30	16	0.057
L480592		0.13	<10	<10	48	10	10	0.007
L480593		0.13	<10	<10	32	10	17	0.026
L480594		0.14	<10	<10	38	10	13	0.023
L480595		0.15	<10	<10	101	20	145	0.703
L480596		0.13	<10	<10	34	20	12	0.024
L480597		0.13	<10	<10	61	20	17	0.014
L480598		0.10	<10	<10	32	20	15	0.018



ALS Canada Ltd.
 2103 Dollarton Hwy
 North Vancouver BC V7H 0A7
 Téléphone: 604 984 0221 Télécopieur: 604 984 0218
 www.alsglobal.com

À: PAGET MINERALS CORPORATION
 1160 - 1040 W. GEORGIA ST.
 VANCOUVER BC V6E 4H1

Page: 3 - A
 Nombre total de pages: 6 (A - C)

Finalisée date:
 13-AOUT-2011
 Compte: PAGMIN

Projet: Icy Lake

CERTIFICAT D'ANALYSE TR11138182

Description échantillon	Méthode élément unités L.D.	WEI-21	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41
		Poids reçu kg	Ag ppm	Al %	As ppm	B ppm	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	Ga ppm
L480599		5.17	0.4	0.88	5	<10	40	<0.5	3	1.32	<0.5	12	84	646	2.48	<10
L480600		4.38	0.6	0.91	6	<10	60	<0.5	2	0.97	<0.5	15	59	826	2.13	<10
L480601		4.52	1.2	0.50	5	<10	40	<0.5	8	0.95	<0.5	10	18	2430	1.12	<10
L480602		4.65	1.2	0.56	4	<10	50	<0.5	5	0.93	<0.5	6	33	1080	1.47	<10
L480603		4.86	0.6	0.56	4	<10	40	<0.5	7	0.98	<0.5	10	24	728	1.29	<10
L480604		4.85	0.5	0.62	2	<10	50	<0.5	7	0.96	<0.5	8	35	695	1.47	<10
L480605		0.08	0.2	1.52	4	<10	140	<0.5	<2	0.92	<0.5	7	41	29	3.14	<10
L480606		5.59	0.3	0.76	3	<10	50	<0.5	<2	0.94	<0.5	6	58	358	1.92	<10
L480607		4.63	0.8	0.63	5	<10	40	<0.5	5	0.97	<0.5	7	38	1025	1.88	<10
L480608		4.95	0.2	0.60	2	<10	50	<0.5	2	0.91	<0.5	5	40	187	1.83	<10
L480609		4.42	<0.2	0.61	<2	<10	40	<0.5	3	1.02	<0.5	6	43	327	1.47	<10
L480610		5.40	0.8	0.72	2	<10	40	<0.5	<2	1.10	<0.5	7	30	1165	1.34	<10
L480611		4.29	0.9	0.72	3	<10	40	<0.5	<2	1.08	<0.5	9	34	1385	1.37	<10
L480612		4.88	0.8	0.72	5	<10	40	<0.5	<2	1.18	<0.5	8	30	1085	1.28	<10
L480613		4.62	1.5	0.63	11	<10	40	<0.5	2	1.65	<0.5	5	23	1415	1.05	<10
L480614		4.61	2.3	0.39	250	<10	270	0.5	2	3.82	1.0	14	8	718	2.33	<10
L480615		0.08	1.8	1.24	15	<10	130	<0.5	<2	0.69	<0.5	7	31	3360	3.19	<10
L480616		4.94	0.9	0.68	87	<10	90	<0.5	2	2.27	<0.5	8	23	653	1.32	<10
L480617		4.88	0.7	0.68	6	<10	40	<0.5	<2	1.21	<0.5	13	23	1075	1.37	<10
L480618		4.48	0.4	0.72	4	<10	50	<0.5	<2	1.24	<0.5	8	31	663	1.37	<10
L480619		4.77	3.0	0.76	3	<10	50	<0.5	3	1.11	<0.5	6	31	805	1.08	<10
L480620		4.77	0.4	0.41	2	<10	60	<0.5	3	1.06	<0.5	3	17	635	0.51	<10
L480621		4.33	0.7	0.71	4	<10	80	<0.5	2	1.64	<0.5	5	27	1110	0.95	<10
L480622		4.93	0.6	0.77	5	<10	50	<0.5	<2	1.31	<0.5	7	35	641	1.50	<10
L480623		4.83	0.6	0.78	4	<10	40	<0.5	3	1.19	<0.5	8	39	942	1.66	<10
L480624		4.98	0.4	0.82	5	<10	50	<0.5	2	1.74	<0.5	9	40	557	1.80	<10
L480625		0.08	0.2	1.06	4	<10	90	<0.5	<2	0.66	<0.5	7	30	22	2.04	<10
L480626		5.31	0.8	0.73	98	<10	410	<0.5	2	2.29	1.0	11	32	711	2.30	<10
L480627		4.77	<0.2	0.75	5	<10	50	<0.5	<2	1.03	<0.5	9	38	350	1.91	<10
L480628		5.14	0.5	0.75	5	<10	50	<0.5	2	0.98	<0.5	9	37	642	1.46	<10
L480629		5.13	0.6	0.59	5	<10	40	<0.5	2	0.87	<0.5	6	27	665	0.90	<10
L480630		3.85	0.9	0.99	43	<10	70	<0.5	7	2.85	1.4	10	32	887	2.12	<10
L480631		3.76	0.3	0.56	3	<10	60	<0.5	<2	1.08	<0.5	3	19	351	0.50	<10
L480632		3.97	0.2	0.60	2	<10	50	<0.5	<2	1.11	<0.5	3	20	236	0.61	<10
L480633		5.66	0.8	0.63	7	<10	50	<0.5	<2	1.42	<0.5	9	31	885	1.37	<10
L480634		4.72	0.3	0.46	3	<10	40	<0.5	<2	0.97	<0.5	5	21	306	0.84	<10
L480635		0.08	1.9	1.51	29	<10	110	<0.5	2	1.81	0.9	15	63	1860	4.00	<10
L480636		4.99	0.4	0.56	5	<10	60	<0.5	5	0.88	<0.5	7	26	631	1.24	<10
L480637		4.41	0.6	0.71	7	<10	80	<0.5	2	1.24	<0.5	12	36	703	2.01	<10
L480638		5.25	1.7	0.93	13	<10	40	<0.5	51	2.78	<0.5	20	33	2520	2.15	<10



ALS Canada Ltd.

2103 Dollarton Hwy
 North Vancouver BC V7H 0A7
 Téléphone: 604 984 0221 Télécopieur: 604 984 0218
 www.alsglobal.com

À: PAGET MINERALS CORPORATION
 1160 - 1040 W. GEORGIA ST.
 VANCOUVER BC V6E 4H1

Page: 3 - B
 Nombre total de pages: 6 (A - C)

Finalisée date:
 13-AOUT-2011
 Compte: PAGMIN

Projet: Icy Lake

CERTIFICAT D'ANALYSE TR11138182

Description échantillon	Méthode élément unités L.D.	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41
		Hg ppm 1	K % 0.01	La ppm 10	Mg % 0.01	Mn ppm 5	Mo ppm 1	Na % 0.01	Ni ppm 1	P ppm 10	Pb ppm 2	S % 0.01	Sb ppm 2	Sc ppm 1	Sr ppm 1
L480599	<1	0.24	10	0.74	154	140	0.10	23	1200	<2	0.37	<2	3	44	<20
L480600	<1	0.34	<10	0.68	129	68	0.09	28	1040	<2	0.50	<2	2	55	<20
L480601	<1	0.11	<10	0.19	62	132	0.07	21	840	9	0.57	<2	1	28	<20
L480602	<1	0.11	10	0.26	74	213	0.07	13	900	4	0.37	<2	1	38	<20
L480603	<1	0.09	<10	0.20	62	376	0.07	15	870	5	0.49	<2	1	53	<20
L480604	<1	0.11	<10	0.24	74	444	0.09	14	940	3	0.37	<2	1	41	<20
L480605	<1	0.16	10	0.53	444	6	0.20	22	480	<2	0.04	<2	5	55	<20
L480606	<1	0.21	10	0.50	101	149	0.09	18	1040	<2	0.21	<2	2	57	<20
L480607	<1	0.08	<10	0.22	65	174	0.09	14	960	<2	0.37	<2	1	68	<20
L480608	<1	0.10	10	0.25	73	202	0.10	14	970	<2	0.25	<2	1	73	<20
L480609	<1	0.10	<10	0.31	80	164	0.09	15	990	<2	0.33	<2	2	58	<20
L480610	<1	0.10	<10	0.23	64	239	0.08	15	940	2	0.44	<2	1	74	<20
L480611	<1	0.10	<10	0.27	74	252	0.08	19	970	<2	0.46	<2	2	103	<20
L480612	<1	0.11	10	0.32	84	230	0.08	16	940	<2	0.40	<2	2	78	<20
L480613	<1	0.14	10	0.47	176	300	0.06	13	890	4	0.37	15	3	38	<20
L480614	<1	0.24	10	1.28	655	219	0.01	19	850	23	0.88	122	10	91	<20
L480615	<1	0.10	10	0.56	425	309	0.09	28	520	21	0.41	3	4	36	<20
L480616	<1	0.15	10	0.53	222	314	0.05	16	900	4	0.40	51	5	52	<20
L480617	<1	0.10	<10	0.34	88	324	0.08	19	910	3	0.55	<2	2	65	<20
L480618	<1	0.13	<10	0.46	111	188	0.08	17	910	<2	0.35	<2	2	94	<20
L480619	<1	0.17	<10	0.43	91	789	0.08	18	910	2	0.27	<2	2	90	<20
L480620	<1	0.15	10	0.35	81	1595	0.05	7	880	4	0.23	<2	1	23	<20
L480621	<1	0.13	<10	0.38	108	770	0.07	13	920	2	0.29	<2	2	47	<20
L480622	<1	0.14	<10	0.37	122	168	0.10	17	910	<2	0.32	<2	3	52	<20
L480623	<1	0.15	<10	0.44	110	269	0.09	19	980	2	0.41	<2	3	46	<20
L480624	<1	0.17	10	0.50	150	191	0.09	20	950	<2	0.43	<2	4	134	<20
L480625	<1	0.06	<10	0.49	308	4	0.06	20	490	2	0.04	<2	4	30	<20
L480626	<1	0.18	10	0.60	437	226	0.06	21	970	23	0.64	59	5	92	<20
L480627	<1	0.18	<10	0.43	90	122	0.11	20	1020	<2	0.49	<2	2	43	<20
L480628	<1	0.19	10	0.41	75	316	0.10	21	970	2	0.57	<2	2	49	<20
L480629	<1	0.11	<10	0.30	60	501	0.09	16	970	<2	0.38	<2	2	40	<20
L480630	<1	0.21	10	0.58	346	312	0.07	22	910	34	0.74	14	5	69	<20
L480631	<1	0.18	10	0.33	71	225	0.08	8	880	3	0.13	<2	1	31	<20
L480632	<1	0.19	10	0.41	77	634	0.08	8	1010	2	0.15	<2	2	32	<20
L480633	<1	0.16	10	0.47	127	370	0.09	17	930	2	0.52	<2	2	41	<20
L480634	<1	0.13	10	0.28	78	216	0.09	10	950	<2	0.23	<2	1	62	<20
L480635	1	0.51	20	0.82	349	152	0.06	15	700	19	1.89	6	6	72	<20
L480636	<1	0.21	10	0.37	80	284	0.09	13	880	3	0.43	<2	1	36	<20
L480637	<1	0.28	10	0.61	144	502	0.09	18	1140	5	0.70	<2	3	46	<20
L480638	<1	0.16	10	0.80	267	262	0.07	18	940	8	0.80	2	6	43	<20



ALS Canada Ltd.
 2103 Dollarton Hwy
 North Vancouver BC V7H 0A7
 Téléphone: 604 984 0221 Télécopieur: 604 984 0218
 www.alsglobal.com

À: PAGET MINERALS CORPORATION
 1160 - 1040 W. GEORGIA ST.
 VANCOUVER BC V6E 4H1

Page: 3 - C
 Nombre total de pages: 6 (A - C)

Finalisée date:
 13-AOUT-2011
 Compte: PAGMIN

Projet: Icy Lake

CERTIFICAT D'ANALYSE TR11138182

Description échantillon	Méthode élément unités L.D.	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	Au-ICP21
		Ti %	Ti ppm	U ppm	V ppm	W ppm	Zn ppm	Au ppm
		0.01	10	10	1	10	2	0.001
L480599		0.23	<10	<10	101	20	21	0.013
L480600		0.19	<10	<10	74	30	22	0.024
L480601		0.13	<10	<10	32	40	27	0.058
L480602		0.13	<10	<10	53	10	21	0.026
L480603		0.12	<10	<10	38	20	12	0.054
L480604		0.14	<10	<10	53	10	16	0.045
L480605		0.15	<10	<10	56	10	36	<0.001
L480606		0.17	<10	<10	72	10	16	0.015
L480607		0.13	<10	<10	60	10	14	0.020
L480608		0.15	<10	<10	63	40	9	0.004
L480609		0.13	<10	<10	55	20	10	0.007
L480610		0.13	<10	<10	50	10	14	0.017
L480611		0.13	<10	<10	50	120	15	0.022
L480612		0.13	<10	<10	50	30	13	0.017
L480613		0.12	<10	<10	43	20	21	0.016
L480614		<0.01	<10	<10	29	<10	62	0.218
L480615		0.11	<10	<10	52	<10	54	1.025
L480616		0.07	<10	<10	45	<10	33	0.064
L480617		0.13	<10	<10	46	10	13	0.017
L480618		0.14	<10	<10	54	10	14	0.011
L480619		0.15	<10	<10	53	<10	14	0.015
L480620		0.14	<10	<10	33	<10	10	0.008
L480621		0.12	<10	<10	45	10	13	0.016
L480622		0.14	<10	<10	59	10	12	0.008
L480623		0.14	<10	<10	67	10	14	0.014
L480624		0.13	<10	<10	65	10	13	0.008
L480625		0.11	<10	<10	47	10	34	0.003
L480626		0.08	<10	<10	56	<10	68	0.025
L480627		0.18	<10	<10	71	<10	11	0.006
L480628		0.17	<10	<10	58	10	13	0.012
L480629		0.14	<10	<10	44	10	11	0.015
L480630		0.10	<10	<10	62	10	77	0.023
L480631		0.16	<10	<10	36	<10	10	0.005
L480632		0.17	<10	<10	46	<10	12	0.005
L480633		0.15	<10	<10	54	10	16	0.013
L480634		0.14	<10	<10	40	10	8	0.004
L480635		0.04	<10	<10	57	<10	65	0.183
L480636		0.15	<10	<10	49	<10	14	0.011
L480637		0.17	<10	<10	81	<10	21	0.017
L480638		0.11	<10	<10	70	10	32	0.027



ALS Canada Ltd.
 2103 Dollarton Hwy
 North Vancouver BC V7H 0A7
 Téléphone: 604 984 0221 Télécopieur: 604 984 0218
 www.alsglobal.com

À: PAGET MINERALS CORPORATION
 1160 - 1040 W. GEORGIA ST.
 VANCOUVER BC V6E 4H1

Page: 4 - A
 Nombre total de pages: 6 (A - C)

Finalisée date:
 13-AOUT-2011
 Compte: PAGMIN

Projet: Icy Lake

CERTIFICAT D'ANALYSE TR11138182

Description échantillon	Méthode élément unités L.D.	WEI-21	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41
		Poids reçu kg	Ag ppm	Al %	As ppm	B ppm	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	Ga ppm
		0.02	0.2	0.01	2	10	10	0.5	2	0.01	0.5	1	1	1	0.01	10
L480639		5.36	0.6	0.59	3	<10	60	<0.5	15	1.56	<0.5	10	10	870	1.27	<10
L480640		4.70	0.8	0.69	34	<10	210	<0.5	3	2.55	<0.5	9	11	1230	1.71	<10
L480641		4.52	0.8	0.58	7	<10	50	<0.5	<2	0.84	<0.5	8	13	879	1.39	<10
L480642		4.73	1.2	0.90	6	<10	40	<0.5	52	1.31	<0.5	14	41	1270	1.63	<10
L480643		5.48	0.8	1.04	5	<10	50	<0.5	2	1.27	<0.5	12	53	1225	1.89	<10
L480644		5.21	0.9	0.85	6	<10	40	<0.5	5	1.16	<0.5	10	34	866	1.60	<10
L480645		0.07	0.2	0.99	4	<10	70	<0.5	<2	0.62	<0.5	7	30	28	1.97	<10
L480646		4.68	0.6	0.93	5	<10	70	<0.5	2	1.01	<0.5	11	44	577	1.95	<10
L480647		5.46	0.9	0.75	4	<10	60	<0.5	2	2.16	<0.5	10	38	920	1.44	<10
L480648		3.18	0.8	0.80	5	<10	110	<0.5	<2	2.77	<0.5	13	37	786	1.93	<10
L480649		4.00	1.2	0.96	19	<10	250	0.5	97	8.7	<0.5	12	26	618	2.00	<10
L480650		5.20	0.8	1.00	5	<10	330	<0.5	6	3.34	<0.5	16	45	987	2.81	<10
L480651		5.16	0.7	0.79	8	<10	50	<0.5	<2	1.44	<0.5	10	32	694	1.45	<10
L480652		4.95	1.0	0.94	10	<10	80	<0.5	9	2.82	<0.5	10	35	965	1.92	<10
L480653		5.58	0.9	0.62	10	<10	40	<0.5	13	1.33	<0.5	9	24	868	1.54	<10
L480654		5.36	0.5	0.69	6	<10	50	<0.5	4	0.96	<0.5	8	24	506	1.47	<10
L480655		0.08	3.6	1.71	38	<10	120	<0.5	<2	0.99	1.1	18	58	9310	4.46	10
L480656		5.22	1.4	0.52	30	<10	320	<0.5	14	2.07	2.2	7	18	665	1.18	<10
L480657		5.16	0.7	0.58	4	<10	30	<0.5	18	1.02	<0.5	7	18	720	1.19	<10
L480658		4.61	0.7	0.73	5	<10	30	<0.5	2	1.18	<0.5	11	29	948	2.14	<10
L480659		5.07	0.7	0.56	5	<10	30	<0.5	3	1.08	<0.5	8	19	814	1.06	<10
L480660		5.10	4.5	0.66	4	<10	50	<0.5	11	1.04	<0.5	12	21	1305	1.50	<10
L480661		2.33	0.3	1.22	23	<10	150	<0.5	2	2.42	<0.5	12	34	424	2.33	<10
L480662		3.98	1.0	0.64	146	<10	260	0.5	<2	4.04	0.5	8	11	357	1.98	<10
L480663		5.21	0.5	0.62	3	<10	110	<0.5	2	1.67	<0.5	6	26	573	1.08	<10
L480664		5.23	0.7	0.44	6	<10	30	<0.5	4	1.07	<0.5	6	14	748	0.75	<10
L480665		0.08	0.2	0.98	5	<10	80	<0.5	<2	0.62	<0.5	7	30	22	1.98	<10
L480666		5.39	0.5	0.50	4	<10	160	<0.5	7	1.20	<0.5	6	6	587	1.48	<10
L480667		4.76	0.5	0.36	4	<10	80	<0.5	17	0.83	<0.5	4	9	544	1.00	<10
L480668		4.68	0.2	0.44	3	<10	60	<0.5	16	0.82	<0.5	4	13	269	0.80	<10
L480669		5.48	0.3	0.32	3	<10	50	<0.5	8	0.93	<0.5	3	12	348	0.51	<10
L480670		4.98	0.4	0.45	17	<10	80	<0.5	4	1.39	<0.5	3	12	364	0.65	<10
L480671		4.56	0.3	0.43	3	<10	40	<0.5	3	0.74	<0.5	4	22	327	0.86	<10
L480672		5.07	0.2	0.35	3	<10	50	<0.5	8	0.61	<0.5	3	16	239	0.45	<10
L480673		5.17	0.7	0.57	3	<10	50	<0.5	3	0.93	<0.5	6	24	631	1.15	<10
L480674		5.08	0.8	0.57	79	<10	170	<0.5	3	2.29	<0.5	7	20	547	1.62	<10
L480675		0.08	1.6	1.30	15	<10	140	<0.5	<2	0.73	<0.5	7	32	3440	3.29	<10
L480676		5.21	0.3	0.62	3	<10	60	<0.5	<2	0.96	<0.5	5	28	266	1.20	<10
L480677		4.82	0.4	0.34	2	<10	40	<0.5	2	0.64	<0.5	3	17	396	0.65	<10
L480678		5.19	0.6	0.45	23	<10	220	<0.5	<2	2.33	<0.5	4	18	415	0.93	<10



ALS Canada Ltd.
2103 Dollarton Hwy
North Vancouver BC V7H 0A7
Téléphone: 604 984 0221 Télécopieur: 604 984 0218
www.alsglobal.com

À: PAGET MINERALS CORPORATION
1160 - 1040 W. GEORGIA ST.
VANCOUVER BC V6E 4H1

Page: 4 - B
Nombre total de pages: 6 (A - C)
Finalisée date:
13-AOUT-2011
Compte: PAGMIN

Projet: Icy Lake

CERTIFICAT D'ANALYSE TR11138182

Description échantillon	Méthode élément unités L.D.	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	
		Hg ppm 1	K % 0.01	La ppm 10	Mg % 0.01	Mn ppm 5	Mo ppm 1	Na % 0.01	Ni ppm 1	P ppm 10	Pb ppm 2	S % 0.01	Sb ppm 2	Sc ppm 1	Sr ppm 1	Th ppm 20
L480639		<1	0.19	10	0.51	150	418	0.09	8	830	4	0.48	<2	2	39	<20
L480640		<1	0.18	10	0.68	231	160	0.07	8	770	3	0.52	7	3	53	<20
L480641		<1	0.16	<10	0.33	83	121	0.10	8	770	4	0.57	<2	2	34	<20
L480642		<1	0.17	<10	0.46	94	108	0.11	21	980	5	0.70	<2	2	43	<20
L480643		<1	0.23	<10	0.64	116	110	0.12	22	930	3	0.44	<2	4	45	<20
L480644		<1	0.21	<10	0.57	92	267	0.10	20	780	4	0.64	<2	3	37	<20
L480645		<1	0.06	<10	0.47	301	6	0.05	21	480	2	0.04	<2	4	27	<20
L480646		<1	0.41	<10	0.77	120	200	0.11	19	880	3	0.51	<2	4	37	<20
L480647		<1	0.19	<10	0.82	169	87	0.10	17	830	2	0.41	<2	5	79	<20
L480648		<1	0.17	10	0.83	210	317	0.11	25	970	2	0.80	<2	7	87	<20
L480649		<1	0.16	10	0.77	702	564	0.03	20	860	40	0.66	10	10	112	<20
L480650		<1	0.15	10	1.13	280	391	0.09	30	980	3	0.84	<2	9	122	<20
L480651		<1	0.19	<10	0.69	108	99	0.10	23	1000	5	0.60	<2	3	44	<20
L480652		<1	0.19	10	0.92	188	434	0.10	21	970	4	0.67	<2	6	59	<20
L480653		<1	0.17	<10	0.56	103	195	0.10	16	850	3	0.57	3	3	41	<20
L480654		<1	0.19	<10	0.60	82	535	0.11	15	880	3	0.64	<2	3	39	<20
L480655		1	0.51	10	1.03	516	889	0.11	37	880	41	2.14	7	9	47	<20
L480656		1	0.13	10	0.49	140	240	0.07	13	820	145	0.53	29	3	67	<20
L480657		<1	0.10	<10	0.30	66	135	0.10	12	870	5	0.64	<2	2	38	<20
L480658		<1	0.12	<10	0.50	104	111	0.11	18	820	3	0.90	<2	2	44	<20
L480659		<1	0.11	10	0.33	78	287	0.10	16	880	5	0.53	2	2	42	<20
L480660		<1	0.16	<10	0.50	97	236	0.09	16	860	3	0.73	<2	2	47	<20
L480661		<1	0.35	10	0.85	215	212	0.05	23	850	3	0.47	16	14	157	<20
L480662		<1	0.27	10	1.20	490	147	0.02	16	730	47	0.48	67	12	123	<20
L480663		<1	0.16	<10	0.51	110	128	0.10	16	790	6	0.36	<2	4	57	<20
L480664		<1	0.10	<10	0.25	72	296	0.09	10	730	5	0.44	<2	1	37	<20
L480665		<1	0.06	<10	0.47	303	4	0.05	21	480	2	0.04	<2	3	28	<20
L480666		<1	0.12	20	0.34	133	109	0.09	6	1100	7	0.62	<2	2	65	<20
L480667		<1	0.13	10	0.16	76	188	0.08	5	910	6	0.52	<2	1	44	<20
L480668		<1	0.14	<10	0.14	49	233	0.09	7	780	6	0.57	<2	1	38	<20
L480669		<1	0.11	<10	0.19	61	238	0.08	6	760	8	0.29	<2	1	27	<20
L480670		<1	0.13	10	0.36	98	301	0.07	6	750	7	0.28	18	2	38	<20
L480671		<1	0.12	<10	0.17	57	154	0.11	9	790	4	0.31	<2	1	32	<20
L480672		<1	0.13	<10	0.13	41	129	0.10	5	720	5	0.16	<2	1	24	<20
L480673		<1	0.15	10	0.41	101	113	0.12	15	730	7	0.44	<2	2	35	<20
L480674		<1	0.20	10	0.56	215	369	0.07	14	730	8	0.89	39	4	65	<20
L480675		<1	0.11	10	0.57	438	311	0.09	28	530	20	0.44	4	5	38	<20
L480676		<1	0.18	10	0.39	106	262	0.11	10	750	4	0.36	<2	2	34	<20
L480677		<1	0.13	10	0.17	61	331	0.09	6	450	5	0.28	<2	1	27	<20
L480678		<1	0.17	10	0.42	208	324	0.06	8	590	6	0.25	14	4	75	<20



ALS Canada Ltd.
 2103 Dollarton Hwy
 North Vancouver BC V7H 0A7
 Téléphone: 604 984 0221 Télécopieur: 604 984 0218
 www.alsglobal.com

À: PAGET MINERALS CORPORATION
 1160 - 1040 W. GEORGIA ST.
 VANCOUVER BC V6E 4H1

Page: 4 - C
 Nombre total de pages: 6 (A - C)
 Finalisée date:
 13-AOUT-2011
 Compte: PAGMIN

Projet: Icy Lake

CERTIFICAT D'ANALYSE TR11138182

Description échantillon	Méthode élément unités L.D.	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	Au-ICP21
		Ti %	Ti ppm	U ppm	V ppm	W ppm	Zn ppm	Au ppm
		0.01	10	10	1	10	2	0.001
L480639		0.12	<10	<10	45	20	16	0.015
L480640		0.08	<10	<10	45	<10	22	0.022
L480641		0.13	<10	<10	42	10	17	0.011
L480642		0.15	<10	<10	61	10	19	0.017
L480643		0.17	<10	<10	80	<10	23	0.012
L480644		0.13	<10	<10	57	<10	20	0.024
L480645		0.10	<10	<10	45	10	34	<0.001
L480646		0.17	<10	<10	76	<10	23	0.014
L480647		0.14	<10	<10	65	<10	27	0.025
L480648		0.13	<10	<10	74	<10	25	0.024
L480649		0.01	<10	<10	59	<10	33	0.015
L480650		0.11	<10	<10	95	<10	29	0.027
L480651		0.15	<10	<10	57	<10	21	0.032
L480652		0.12	<10	<10	85	10	28	0.023
L480653		0.13	<10	<10	54	10	18	0.017
L480654		0.15	<10	<10	56	<10	14	0.012
L480655		0.14	<10	<10	101	20	153	0.624
L480656		0.10	<10	<10	37	10	160	0.053
L480657		0.13	<10	<10	40	10	11	0.012
L480658		0.14	<10	<10	61	<10	18	0.016
L480659		0.14	<10	<10	41	20	14	0.013
L480660		0.15	<10	<10	49	20	18	0.021
L480661		0.07	<10	<10	86	<10	31	0.011
L480662		0.01	<10	<10	39	<10	45	0.187
L480663		0.14	<10	<10	55	10	17	0.025
L480664		0.11	<10	<10	27	20	13	0.022
L480665		0.10	<10	<10	45	10	35	<0.001
L480666		0.12	<10	<10	42	10	16	0.006
L480667		0.12	<10	<10	26	10	11	0.008
L480668		0.12	<10	<10	23	10	9	0.006
L480669		0.12	<10	<10	21	10	11	0.009
L480670		0.10	<10	<10	25	10	13	0.006
L480671		0.13	<10	<10	32	10	10	0.008
L480672		0.13	<10	<10	22	10	7	0.002
L480673		0.14	<10	<10	44	20	16	0.010
L480674		0.08	<10	<10	38	<10	31	0.043
L480675		0.12	<10	<10	54	<10	55	0.997
L480676		0.14	<10	<10	47	<10	12	0.006
L480677		0.09	<10	<10	20	10	9	0.011
L480678		0.07	<10	<10	32	20	16	0.012



ALS Canada Ltd.

2103 Dollarton Hwy
North Vancouver BC V7H 0A7
Téléphone: 604 984 0221 Télécopieur: 604 984 0218
www.alsglobal.com

À: PAGET MINERALS CORPORATION
1160 - 1040 W. GEORGIA ST.
VANCOUVER BC V6E 4H1

Page: 5 - A
Nombre total de pages: 6 (A - C)

Finalisée date:
13-AOUT-2011
Compte: PAGMIN

Projet: Icy Lake

CERTIFICAT D'ANALYSE TR11138182

Description échantillon	Méthode	WEI-21	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41
	élément	Poids reçu	Ag	Al	As	B	Ba	Be	Bi	Ca	Cd	Co	Cr	Cu	Fe	Ga
	unités	kg	ppm	%	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	%	ppm
	L.D.	0.02	0.2	0.01	2	10	10	0.5	2	0.01	0.5	1	1	1	0.01	10
L480679		5.30	0.4	0.36	3	<10	40	<0.5	<2	0.75	<0.5	3	17	417	0.74	<10
L480680		5.16	0.6	0.36	7	<10	40	<0.5	9	1.11	<0.5	3	15	408	0.69	<10
L480681		5.00	0.9	0.51	24	<10	250	<0.5	4	1.89	<0.5	5	18	667	1.14	<10
L480682		4.11	0.5	0.36	4	<10	40	<0.5	2	0.88	<0.5	2	13	592	0.41	<10
L480683		3.65	0.2	0.36	<2	<10	50	<0.5	8	1.29	<0.5	2	13	143	0.53	<10
L480684		5.06	0.4	0.49	21	<10	160	<0.5	41	3.41	<0.5	4	9	223	1.57	<10
L480685		0.08	0.5	1.11	4	<10	90	<0.5	<2	0.69	<0.5	7	31	21	2.08	<10
L480686		5.23	32.7	0.52	108	<10	80	<0.5	7	1.34	14.6	5	20	1125	1.50	<10
L480687		4.98	0.9	0.45	6	<10	40	<0.5	23	1.29	<0.5	6	19	835	1.30	<10
L480688		5.32	0.4	0.63	6	<10	60	<0.5	<2	1.22	<0.5	5	26	326	1.54	<10
L480689		5.37	0.4	0.54	3	<10	60	<0.5	3	0.94	<0.5	4	26	297	1.28	<10
L480690		5.37	0.7	1.25	7	<10	110	<0.5	12	2.19	<0.5	9	53	507	2.63	<10
L480691		5.40	0.5	0.59	2	<10	50	<0.5	5	1.17	<0.5	5	30	433	1.33	<10
L480692		5.16	0.4	0.59	4	<10	40	<0.5	3	1.00	<0.5	4	22	360	1.05	<10
L480693		5.30	0.3	0.59	3	<10	50	<0.5	4	1.00	<0.5	5	25	292	1.07	<10
L480694		5.31	2.1	1.69	29	<10	90	0.5	3	1.92	0.9	16	68	2010	4.27	<10
L480695		0.08	2.0	1.50	26	<10	100	<0.5	<2	1.71	0.8	14	61	1790	3.81	<10
L480696		5.18	0.4	0.71	2	<10	60	<0.5	14	0.94	<0.5	7	52	327	1.41	<10
L480697		5.16	0.2	0.94	3	<10	50	<0.5	<2	1.23	<0.5	7	55	190	1.68	<10
L480698		3.50	0.3	0.96	<2	<10	50	<0.5	16	1.31	<0.5	8	47	306	1.98	<10
L480699		2.78	0.5	0.59	3	<10	70	<0.5	21	1.70	<0.5	7	5	195	2.32	<10
L480700		4.94	<0.2	0.93	3	<10	50	<0.5	10	1.50	<0.5	7	35	186	1.57	<10
L480701		5.13	0.2	0.85	4	<10	50	<0.5	4	1.34	<0.5	6	36	279	1.56	<10
L480702		5.25	0.5	0.89	3	<10	60	<0.5	12	1.19	<0.5	9	37	570	1.63	<10
L480703		5.43	0.3	0.90	2	<10	80	<0.5	<2	0.81	<0.5	8	41	227	1.53	<10
L480704		5.46	0.3	0.79	4	<10	60	<0.5	12	1.00	<0.5	9	29	268	1.54	<10
L480705		0.08	0.2	1.08	4	<10	90	<0.5	<2	0.67	<0.5	6	31	21	2.01	<10
L480706		5.43	0.3	0.89	4	<10	70	<0.5	9	1.12	<0.5	7	38	390	1.54	<10
L480707		5.01	0.3	0.91	5	<10	60	<0.5	13	1.51	<0.5	7	49	219	1.66	<10
L480708		5.35	0.2	0.80	4	<10	50	<0.5	2	1.34	<0.5	5	24	226	1.32	<10
L480709		4.26	0.2	0.72	6	<10	40	<0.5	11	1.09	<0.5	7	27	246	1.56	<10
L480710		4.23	<0.2	0.87	3	<10	90	<0.5	<2	2.87	<0.5	6	25	232	2.09	<10
L480711		2.65	2.4	0.47	44	<10	60	<0.5	4	5.63	0.8	9	5	136	2.32	<10
L480712		4.91	0.3	0.88	4	<10	40	<0.5	6	1.32	<0.5	7	37	217	2.64	<10
L480713		5.06	0.2	0.86	3	<10	50	<0.5	24	1.23	<0.5	6	29	208	1.58	<10
L480714		4.95	0.2	1.00	3	<10	60	<0.5	7	1.23	<0.5	9	45	262	1.79	<10
L480715		0.08	3.6	1.81	35	<10	110	<0.5	<2	1.02	1.1	18	60	9770	4.72	10
L480716		4.87	0.3	0.88	3	<10	70	<0.5	8	1.12	<0.5	9	39	318	1.72	<10
L480717		4.87	1.9	0.71	3	<10	40	<0.5	53	1.40	<0.5	11	37	1730	2.05	<10
L480718		5.08	0.2	0.83	3	<10	60	<0.5	13	1.15	<0.5	9	35	270	1.65	<10



ALS Canada Ltd.

2103 Dollarton Hwy
North Vancouver BC V7H 0A7
Téléphone: 604 984 0221 Télécopieur: 604 984 0218
www.alsglobal.com

À: PAGET MINERALS CORPORATION
1160 - 1040 W. GEORGIA ST.
VANCOUVER BC V6E 4H1

Page: 5 - B
Nombre total de pages: 6 (A - C)

Finalisée date:
13-AOUT-2011
Compte: PAGMIN

Projet: icy Lake

CERTIFICAT D'ANALYSE TR11138182

Description échantillon	Méthode élément unités L.D.	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	
		Hg	K	La	Mg	Mn	Mo	Na	Ni	P	Pb	S	Sb	Sc	Sr	Th
		ppm	%	ppm	%	ppm	ppm	%	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm
L480679		<1	0.11	<10	0.27	69	188	0.09	8	710	2	0.24	<2	1	32	<20
L480680		<1	0.11	10	0.30	105	345	0.07	6	720	9	0.27	2	2	38	<20
L480681		<1	0.20	10	0.41	187	240	0.07	10	740	8	0.34	11	3	114	<20
L480682		<1	0.13	<10	0.26	62	71	0.08	4	780	5	0.14	<2	1	33	<20
L480683		<1	0.13	10	0.38	88	160	0.07	5	770	5	0.16	<2	2	37	<20
L480684		<1	0.12	10	1.12	445	138	0.02	11	720	14	0.44	21	8	76	<20
L480685		<1	0.06	10	0.50	316	3	0.06	20	510	<2	0.05	<2	4	31	<20
L480686		<1	0.14	<10	0.53	239	276	0.05	10	660	905	0.86	416	3	38	<20
L480687		<1	0.13	<10	0.40	118	173	0.07	10	690	3	0.80	<2	2	32	<20
L480688		<1	0.18	10	0.48	137	128	0.11	11	760	2	0.47	<2	2	34	<20
L480689		<1	0.15	<10	0.39	114	91	0.09	9	680	5	0.33	<2	2	29	<20
L480690		<1	0.32	10	0.78	229	173	0.19	19	1530	7	0.72	<2	4	70	<20
L480691		<1	0.12	<10	0.30	97	129	0.09	10	850	2	0.54	<2	2	34	<20
L480692		<1	0.13	<10	0.34	90	82	0.09	8	670	<2	0.19	<2	2	30	<20
L480693		<1	0.17	10	0.35	99	128	0.10	9	820	2	0.25	<2	2	33	<20
L480694		<1	0.55	20	0.88	371	164	0.07	16	760	20	2.05	7	7	78	<20
L480695		<1	0.49	20	0.78	332	149	0.06	15	670	19	1.83	6	6	69	<20
L480696		<1	0.24	<10	0.54	121	49	0.09	23	770	<2	0.33	<2	3	36	<20
L480697		<1	0.16	10	0.58	151	81	0.14	20	940	<2	0.29	<2	3	48	<20
L480698		<1	0.16	10	0.53	131	89	0.11	17	1080	2	0.51	<2	3	36	<20
L480699		<1	0.11	20	0.47	192	19	0.08	5	1160	10	1.21	<2	3	56	<20
L480700		<1	0.13	10	0.57	168	190	0.14	12	910	<2	0.39	<2	3	51	<20
L480701		<1	0.14	10	0.51	135	68	0.13	11	870	<2	0.38	<2	3	50	<20
L480702		<1	0.24	<10	0.58	140	153	0.13	13	770	<2	0.58	<2	3	77	<20
L480703		<1	0.45	10	0.79	131	193	0.12	14	840	<2	0.38	<2	4	51	<20
L480704		<1	0.27	<10	0.59	117	234	0.10	13	690	<2	0.68	<2	3	37	<20
L480705		<1	0.06	10	0.48	306	3	0.06	20	490	<2	0.05	<2	4	30	<20
L480706		<1	0.30	10	0.77	126	273	0.10	16	750	<2	0.59	<2	3	35	<20
L480707		<1	0.21	10	0.72	156	167	0.13	17	920	<2	0.52	<2	4	50	<20
L480708		<1	0.15	10	0.33	109	232	0.12	9	760	<2	0.46	<2	2	57	<20
L480709		<1	0.25	<10	0.60	139	167	0.07	11	790	4	0.63	<2	3	29	<20
L480710		<1	0.21	<10	0.78	322	145	0.05	13	800	2	0.45	<2	5	62	<20
L480711		<1	0.28	<10	0.59	1445	126	0.01	15	700	388	1.86	37	5	157	<20
L480712		<1	0.23	<10	0.88	184	69	0.07	15	850	3	1.51	2	3	35	<20
L480713		<1	0.23	<10	0.56	150	133	0.10	12	770	4	0.46	<2	3	60	<20
L480714		<1	0.32	<10	0.68	144	113	0.11	18	970	3	0.52	<2	3	76	<20
L480715		1	0.53	10	1.05	543	881	0.11	35	920	41	2.16	9	9	50	<20
L480716		1	0.38	10	0.74	147	103	0.10	17	960	4	0.61	<2	3	61	<20
L480717		<1	0.21	<10	0.59	110	146	0.08	21	940	5	1.43	<2	2	56	<20
L480718		<1	0.34	10	0.71	128	83	0.12	19	960	3	0.68	<2	3	39	<20



ALS Canada Ltd.
 2103 Dollarton Hwy
 North Vancouver BC V7H 0A7
 Téléphone: 604 984 0221 Télécopieur: 604 984 0218
 www.alsglobal.com

À: PAGET MINERALS CORPORATION
 1160 - 1040 W. GEORGIA ST.
 VANCOUVER BC V6E 4H1

Page: 5 - C
 Nombre total de pages: 6 (A - C)
 Finalisée date:
 13-AOUT-2011
 Compte: PAGMIN

Projet: Icy Lake

CERTIFICAT D'ANALYSE TR11138182

Description échantillon	Méthode élément unités L.D.	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	Au-ICP21
		Ti %	Ti ppm	U ppm	V ppm	W ppm	Zn ppm	Au ppm
		0.01	10	10	1	10	2	0.001
L480679		0.12	<10	<10	30	10	9	0.011
L480680		0.10	<10	<10	27	<10	13	0.009
L480681		0.09	<10	<10	37	<10	21	0.018
L480682		0.13	<10	<10	25	10	10	0.005
L480683		0.12	<10	<10	30	10	10	0.005
L480684		<0.01	<10	<10	29	<10	24	0.004
L480685		0.12	<10	<10	48	10	35	<0.001
L480686		0.07	<10	<10	35	<10	545	0.049
L480687		0.11	<10	<10	36	40	14	0.012
L480688		0.15	<10	<10	52	<10	14	0.004
L480689		0.14	<10	<10	47	<10	12	0.003
L480690		0.26	<10	<10	97	10	24	0.003
L480691		0.13	<10	<10	40	40	10	0.002
L480692		0.14	<10	<10	46	<10	11	0.009
L480693		0.16	<10	<10	43	50	10	0.006
L480694		0.04	<10	<10	62	<10	68	0.003
L480695		0.04	<10	<10	55	<10	62	0.232
L480696		0.15	<10	<10	53	10	14	0.003
L480697		0.17	<10	<10	66	10	15	0.002
L480698		0.19	<10	<10	73	<10	15	0.008
L480699		0.14	<10	<10	58	10	18	0.003
L480700		0.17	<10	<10	65	10	15	0.002
L480701		0.16	<10	<10	59	10	15	0.004
L480702		0.16	<10	<10	60	60	15	0.005
L480703		0.18	<10	<10	69	10	18	0.003
L480704		0.15	<10	<10	54	10	14	0.005
L480705		0.12	<10	<10	47	10	34	0.007
L480706		0.17	<10	<10	65	10	20	0.015
L480707		0.19	<10	<10	69	10	16	0.003
L480708		0.14	<10	<10	45	10	11	0.005
L480709		0.13	<10	<10	52	10	15	0.006
L480710		0.08	<10	<10	57	<10	24	0.003
L480711		<0.01	<10	<10	11	<10	43	0.043
L480712		0.14	<10	<10	64	<10	16	0.004
L480713		0.15	<10	<10	55	10	13	0.003
L480714		0.18	<10	<10	64	<10	16	0.004
L480715		0.15	<10	<10	106	20	154	0.713
L480716		0.19	<10	<10	70	10	19	0.009
L480717		0.16	<10	<10	52	20	16	0.017
L480718		0.20	<10	<10	65	20	16	0.007



ALS Canada Ltd.
 2103 Dollarton Hwy
 North Vancouver BC V7H 0A7
 Téléphone: 604 984 0221 Télécopieur: 604 984 0218
 www.alsglobal.com

À: PAGET MINERALS CORPORATION
 1160 - 1040 W. GEORGIA ST.
 VANCOUVER BC V6E 4H1

Page: 6 - A
 Nombre total de pages: 6 (A - C)

Finalisée date:
 13-AOUT-2011
 Compte: PAGMIN

Projet: Icy Lake

CERTIFICAT D'ANALYSE TR11138182

Description échantillon	Méthode élément unités L.D.	WEI-21	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41
		Poids reçu kg	Ag ppm	Al %	As ppm	B ppm	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	Ga ppm
		0.02	0.2	0.01	2	10	10	0.5	2	0.01	0.5	1	1	1	0.01	10
L480719		4.91	0.4	0.89	4	<10	60	<0.5	6	1.16	<0.5	13	51	462	1.98	<10
L480720		5.01	<0.2	0.83	4	<10	50	<0.5	<2	1.14	<0.5	5	41	170	1.38	<10
L480721		5.35	0.2	0.96	12	<10	70	<0.5	11	1.37	<0.5	7	21	202	1.56	<10
L480722		4.87	0.2	1.02	5	<10	80	<0.5	5	1.37	<0.5	8	29	351	2.17	<10
L480723		5.14	0.3	0.51	5	<10	30	<0.5	6	0.97	<0.5	6	27	286	1.34	<10
L480724		4.96	1.0	0.52	3	<10	30	<0.5	26	1.16	<0.5	7	36	422	1.37	<10
L480725		0.07	<0.2	0.99	5	<10	70	<0.5	<2	0.62	<0.5	6	29	21	1.96	<10
L480726		4.65	0.4	0.74	6	<10	30	<0.5	24	1.71	<0.5	9	25	377	1.91	<10
L480727		3.69	0.3	1.00	3	<10	50	<0.5	<2	2.49	<0.5	7	57	268	1.87	<10
L480728		3.95	0.3	0.96	6	<10	80	<0.5	<2	2.83	<0.5	6	52	213	1.83	<10
L480729		2.03	0.3	0.37	5	<10	140	<0.5	<2	2.95	<0.5	3	11	96	1.39	<10
L480730		1.79	0.2	0.49	3	<10	80	<0.5	<2	2.45	<0.5	4	22	172	1.24	<10



ALS Canada Ltd.
 2103 Dollarton Hwy
 North Vancouver BC V7H 0A7
 Téléphone: 604 984 0221 Télécopieur: 604 984 0218
 www.alsglobal.com

À: PAGET MINERALS CORPORATION
 1160 - 1040 W. GEORGIA ST.
 VANCOUVER BC V6E 4H1

Page: 6 - B
 Nombre total de pages: 6 (A - C)

Finalisée date:
 13-AOUT-2011
 Compte: PAGMIN

Projet: Icy Lake

CERTIFICAT D'ANALYSE TR11138182

Description échantillon	Méthode élément unités L.D.	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	
		Hg ppm	K %	La ppm	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	S %	Sb ppm	Sc ppm	Sr ppm	Th ppm
		1	0.01	10	0.01	5	1	0.01	1	10	2	0.01	2	1	1	20
L480719		<1	0.31	<10	0.67	129	178	0.11	29	970	<2	0.88	<2	3	40	<20
L480720		<1	0.24	10	0.59	126	176	0.10	18	1020	2	0.40	<2	2	38	<20
L480721		<1	0.33	10	0.70	143	329	0.07	13	890	6	0.48	4	4	45	<20
L480722		<1	0.34	10	0.61	215	200	0.11	19	700	2	0.84	<2	3	39	<20
L480723		<1	0.15	10	0.42	97	274	0.09	15	950	<2	0.59	3	2	31	<20
L480724		<1	0.16	10	0.53	124	316	0.07	15	970	12	0.64	<2	2	32	<20
L480725		<1	0.06	<10	0.45	301	4	0.04	20	470	<2	0.05	<2	4	28	<20
L480726		<1	0.20	10	0.81	170	140	0.08	13	980	3	1.01	<2	3	43	<20
L480727		<1	0.36	<10	1.16	277	71	0.09	20	1240	9	0.38	<2	7	50	<20
L480728		1	0.35	10	1.17	365	395	0.06	18	1090	5	0.53	<2	6	72	<20
L480729		<1	0.12	10	0.74	1145	117	0.01	9	470	20	0.50	4	5	53	<20
L480730		<1	0.13	10	0.62	293	414	0.04	13	680	6	0.61	2	4	98	<20



ALS Canada Ltd.
 2103 Dollarton Hwy
 North Vancouver BC V7H 0A7
 Téléphone: 604 984 0221 Télécopieur: 604 984 0218
 www.alsglobal.com

À: PAGET MINERALS CORPORATION
 1160 - 1040 W. GEORGIA ST.
 VANCOUVER BC V6E 4H1

Page: 6 - C
 Nombre total de pages: 6 (A - C)
 Finalisée date:
 13-AOUT-2011
 Compte: PAGMIN

Projet: Icy Lake

CERTIFICAT D'ANALYSE TR11138182

Description échantillon	Méthode élément unités L.D.	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	Au-ICP21
		Ti %	Ti ppm	U ppm	V ppm	W ppm	Zn ppm	Au ppm
		0.01	10	10	1	10	2	0.001
L480719		0.18	<10	<10	63	20	16	0.009
L480720		0.17	<10	<10	60	10	15	0.004
L480721		0.15	<10	<10	70	10	17	0.004
L480722		0.17	<10	<10	80	10	18	0.009
L480723		0.15	<10	<10	47	10	11	0.005
L480724		0.15	<10	<10	47	10	12	0.006
L480725		0.11	<10	<10	45	10	34	0.001
L480726		0.14	<10	<10	57	30	17	0.006
L480727		0.20	<10	<10	92	10	25	0.005
L480728		0.14	<10	<10	77	40	27	0.003
L480729		<0.01	<10	<10	21	<10	20	0.002
L480730		0.08	<10	<10	40	20	18	0.002



ALS Canada Ltd.
2103 Dollarton Hwy
North Vancouver BC V7H 0A7
Téléphone: 604 984 0221 Télécopieur: 604 984 0218
www.alsglobal.com

À: PAGET MINERALS CORPORATION
1160 - 1040 W. GEORGIA ST.
VANCOUVER BC V6E 4H1

Page: 1
Finalisée date: 25-JUIL-2011
Cette copie a fait un rapport sur
9-NOV-2011
Compte: PAGMIN

CERTIFICAT TR11125472

Projet: Icy Lake

Bon de commande #:

Ce rapport s'applique aux 83 échantillons de carotte forage soumis à notre laboratoire de Terrace, BC, Canada le 6-JUIL-2011.

Les résultats sont transmis à:

SONIA JEYACHANDRAN

ROD OGILVIE

DAVID VOLKERT

PRÉPARATION ÉCHANTILLONS

CODE ALS	DESCRIPTION
WEI-21	Poids échantillon reçu
LOG-22	Entrée échantillon - Reçu sans code barre
LOG-23	Entrée pulpe - Reçu avec code barre
CRU-QC	Test concassage QC
PUL-QC	Test concassage QC
CRU-31	Granulation - 70 % <2 mm
SPL-21	Échant. fractionné - div. riffles
PUL-31	Pulvérisé à 85 % <75 um

PROCÉDURES ANALYTIQUES

CODE ALS	DESCRIPTION	INSTRUMENT
Au-ICP21	Au 30 g FA fini ICP-AES	ICP-AES
ME-ICP41	Aqua regia ICP-AES 35 éléments	ICP-AES

À: PAGET MINERALS CORPORATION
ATTN: DAVID VOLKERT
1160 - 1040 W. GEORGIA ST.
VANCOUVER BC V6E 4H1

Ce rapport est final et remplace tout autre rapport préliminaire portant ce numéro de certificat. Les résultats s'appliquent aux échantillons soumis. Toutes les pages de ce rapport ont été vérifiées et approuvées avant publication.

Signature:



Colin Ramshaw, Vancouver Laboratory Manager



ALS Canada Ltd.

2103 Dollarton Hwy
North Vancouver BC V7H 0A7
Téléphone: 604 984 0221 Télécopieur: 604 984 0218
www.alsglobal.com

À: PAGET MINERALS CORPORATION
1160 - 1040 W. GEORGIA ST.
VANCOUVER BC V6E 4H1

Page: 2 - A
Nombre total de pages: 4 (A -
C)
Finalisée date: 25-JUIL-2011
Compte: PAGMIN

Projet: Icy Lake

CERTIFICAT D'ANALYSE TR11125472

Description échantillon	Méthode élément unités L.D.	WEI-21	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	
		Poids reçu kg	Ag ppm	Al %	As ppm	B ppm	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	Ga ppm
		0.02	0.2	0.01	2	10	10	0.5	2	0.01	0.5	1	1	1	0.01	10
L480309		6.04	2.2	0.77	6	<10	40	<0.5	3	0.34	<0.5	18	20	1660	2.90	<10
L480310		7.01	1.3	0.68	5	<10	40	<0.5	2	0.49	<0.5	13	31	1265	2.49	<10
L480311		8.58	0.5	0.71	3	<10	40	<0.5	2	0.62	<0.5	9	14	490	2.43	<10
L480312		9.68	0.4	0.60	4	<10	30	<0.5	<2	0.47	<0.5	7	14	352	1.88	<10
L480313		7.22	0.4	0.72	4	<10	40	<0.5	<2	0.57	<0.5	10	14	466	2.38	<10
L480314		9.02	1.5	0.72	3	<10	40	<0.5	2	0.55	<0.5	13	24	1380	2.60	<10
L480315		0.06	1.7	1.21	14	<10	120	<0.5	<2	0.67	<0.5	7	31	3290	3.26	<10
L480316		9.58	1.1	1.17	5	<10	50	<0.5	<2	0.91	<0.5	20	37	1125	3.71	10
L480317		7.93	1.0	0.94	5	<10	50	<0.5	<2	1.05	<0.5	13	41	991	3.16	<10
L480318		9.65	0.6	1.12	8	<10	40	<0.5	2	1.15	<0.5	17	43	942	3.47	10
L480319		8.38	0.7	1.43	7	<10	50	<0.5	2	1.31	<0.5	13	38	760	3.63	10
L480320		10.07	0.9	0.85	6	<10	40	<0.5	2	0.94	<0.5	19	22	867	3.59	<10
L480321		7.84	1.3	0.97	8	<10	40	<0.5	<2	0.79	<0.5	17	52	1380	3.02	10
L480322		8.57	1.5	0.79	11	<10	40	<0.5	<2	0.80	<0.5	20	73	1600	3.20	<10
L480323		9.20	1.9	0.82	7	<10	30	<0.5	<2	1.30	<0.5	14	70	1500	2.33	<10
L480324		8.58	0.9	0.97	6	<10	30	<0.5	<2	1.62	<0.5	13	33	1010	2.64	10
L480325		0.06	<0.2	1.03	3	<10	80	<0.5	<2	0.63	<0.5	7	31	25	2.00	<10
L480326		9.66	0.5	1.08	4	<10	50	<0.5	<2	1.25	<0.5	12	39	566	3.66	10
L480327		9.96	0.9	0.90	5	<10	30	<0.5	8	1.01	<0.5	13	35	955	3.23	<10
L480328		9.76	1.2	0.86	5	<10	40	<0.5	3	1.03	<0.5	16	30	1215	3.17	<10
L480329		9.05	1.3	1.03	3	<10	40	<0.5	<2	0.93	<0.5	17	38	1950	3.14	10
L480330		9.11	1.4	0.95	4	<10	40	<0.5	<2	0.95	<0.5	15	64	1825	2.72	<10
L480331		9.00	1.4	0.98	6	<10	40	<0.5	<2	0.99	<0.5	23	32	1490	3.06	<10
L480332		7.69	0.5	0.75	3	<10	40	<0.5	<2	0.74	<0.5	8	16	595	1.87	<10
L480333		8.49	0.3	0.64	2	<10	30	<0.5	<2	0.89	<0.5	9	44	418	2.24	<10
L480334		9.70	0.3	0.85	6	<10	40	<0.5	<2	0.94	<0.5	12	29	439	3.15	<10
L480335		0.06	3.8	1.76	39	<10	120	<0.5	9	1.01	1.0	18	58	9360	4.52	10
L480336		8.61	0.2	0.71	4	<10	40	<0.5	3	1.11	<0.5	7	15	246	3.04	<10
L480337		5.29	0.9	0.69	6	<10	40	<0.5	<2	0.97	<0.5	11	17	870	2.72	<10
L480338		4.81	0.4	0.60	2	<10	40	<0.5	<2	0.89	<0.5	7	14	439	2.17	<10
L480339		4.82	0.4	0.73	4	<10	40	<0.5	<2	0.84	<0.5	7	21	390	2.12	<10
L480340		4.96	0.8	0.79	3	<10	40	<0.5	2	0.89	<0.5	11	18	693	2.85	<10
L480341		4.90	0.6	0.81	4	<10	40	<0.5	<2	0.92	<0.5	11	21	570	1.67	<10
L480342		4.10	1.6	0.70	6	<10	40	<0.5	2	1.44	<0.5	12	19	1480	1.99	<10
L480343		5.35	1.0	0.85	5	<10	40	<0.5	2	1.48	<0.5	12	19	1050	2.50	<10
L480344		4.94	1.9	0.80	6	<10	40	<0.5	6	1.22	<0.5	13	26	1760	3.21	<10
L480345		0.06	0.2	1.08	3	<10	80	<0.5	<2	0.68	<0.5	7	31	24	2.07	<10
L480346		4.98	3.7	1.06	6	<10	30	<0.5	11	1.82	<0.5	14	19	2530	3.71	10
L480347		4.74	2.6	1.09	5	<10	20	<0.5	24	2.28	<0.5	16	15	2380	3.89	10
L480348		4.92	2.3	0.91	4	<10	30	<0.5	16	1.63	<0.5	14	12	2010	2.51	<10



ALS Canada Ltd.
 2103 Dollarton Hwy
 North Vancouver BC V7H 0A7
 Téléphone: 604 984 0221 Télécopieur: 604 984 0218
 www.alsglobal.com

À: PAGET MINERALS CORPORATION
 1160 - 1040 W. GEORGIA ST.
 VANCOUVER BC V6E 4H1

Page: 2 - B
 Nombre total de pages: 4 (A - C)
 Finalisée date: 25-JUIL-2011
 Compte: PAGMIN

Projet: Icy Lake

CERTIFICAT D'ANALYSE TR11125472
--

Description échantillon	Méthode élément unités L.D.	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41
		Hg ppm	K %	La ppm	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	S %	Sb ppm	Sc ppm	Sr ppm	Th ppm
		1	0.01	10	0.01	5	1	0.01	1	10	2	0.01	2	1	1	20
L480309		<1	0.15	10	0.49	149	92	0.06	10	680	4	1.24	<2	4	24	<20
L480310		<1	0.14	<10	0.55	143	39	0.08	12	750	3	1.07	<2	3	25	<20
L480311		<1	0.18	<10	0.50	146	30	0.08	8	630	4	0.89	<2	3	25	<20
L480312		<1	0.13	<10	0.37	118	31	0.09	4	530	3	0.67	<2	2	28	<20
L480313		<1	0.17	<10	0.47	144	42	0.09	8	850	3	0.61	<2	2	30	<20
L480314		<1	0.15	<10	0.49	149	40	0.09	11	740	3	1.00	<2	3	28	<20
L480315		<1	0.10	<10	0.55	421	284	0.08	28	510	22	0.41	4	4	38	<20
L480316		<1	0.37	<10	0.88	225	62	0.12	19	1340	2	1.36	<2	5	50	<20
L480317		<1	0.21	<10	0.51	178	36	0.11	18	1420	4	0.76	<2	3	48	<20
L480318		<1	0.28	<10	0.82	216	28	0.12	24	1420	3	1.14	<2	4	131	<20
L480319		<1	0.37	10	1.03	259	41	0.12	18	1760	4	0.72	<2	6	105	<20
L480320		<1	0.21	<10	0.56	175	144	0.10	19	1270	3	1.73	<2	3	39	<20
L480321		<1	0.26	10	0.85	207	23	0.09	45	1330	2	0.97	<2	3	29	<20
L480322		<1	0.17	<10	0.61	147	58	0.09	69	1000	3	1.54	<2	2	29	<20
L480323		<1	0.13	<10	0.51	162	20	0.09	33	1180	2	0.87	<2	3	36	<20
L480324		<1	0.18	<10	0.66	182	43	0.12	16	3380	2	0.94	<2	5	45	<20
L480325		<1	0.06	<10	0.48	303	4	0.05	21	490	3	0.04	<2	4	30	<20
L480326		<1	0.28	10	0.87	260	37	0.12	17	1760	2	0.59	<2	4	36	<20
L480327		<1	0.20	<10	0.65	209	35	0.13	15	1040	3	0.64	<2	5	34	<20
L480328		<1	0.23	<10	0.61	195	267	0.11	16	1340	2	1.04	<2	4	30	<20
L480329		<1	0.43	10	0.88	190	31	0.12	22	1370	4	1.04	<2	5	27	<20
L480330		<1	0.27	10	0.68	162	42	0.11	26	1260	3	1.03	<2	4	33	<20
L480331		<1	0.22	<10	0.53	150	29	0.13	25	1200	6	1.59	<2	3	41	<20
L480332		<1	0.17	<10	0.32	117	25	0.12	6	790	4	0.49	<2	2	34	<20
L480333		<1	0.12	<10	0.26	130	32	0.11	14	960	4	0.46	<2	2	33	<20
L480334		<1	0.22	<10	0.50	182	208	0.12	12	1330	3	0.47	<2	3	36	<20
L480335		<1	0.53	10	1.05	513	917	0.12	35	910	40	2.13	8	9	51	<20
L480336		<1	0.15	10	0.45	180	169	0.11	8	1410	3	0.25	<2	3	43	<20
L480337		<1	0.18	10	0.41	148	23	0.10	11	1340	3	0.74	<2	2	40	<20
L480338		<1	0.14	10	0.34	114	95	0.10	8	1180	4	0.58	<2	2	37	<20
L480339		<1	0.15	<10	0.43	151	68	0.09	8	840	3	0.56	<2	3	38	<20
L480340		<1	0.18	<10	0.46	160	68	0.12	9	890	4	1.01	<2	3	40	<20
L480341		<1	0.15	<10	0.33	115	145	0.12	8	650	4	0.76	<2	3	56	<20
L480342		<1	0.15	<10	0.50	182	527	0.08	10	690	5	0.81	<2	4	36	<20
L480343		<1	0.17	10	0.62	193	179	0.11	12	1400	4	0.78	<2	4	38	<20
L480344		<1	0.16	10	0.50	166	229	0.12	14	1390	3	0.88	<2	3	45	<20
L480345		<1	0.06	<10	0.50	315	4	0.06	20	500	3	0.05	<2	4	32	<20
L480346		<1	0.15	10	0.76	240	92	0.11	14	1610	2	1.13	<2	4	55	<20
L480347		1	0.11	10	0.90	283	151	0.08	11	1450	5	1.36	<2	5	64	<20
L480348		<1	0.14	10	0.65	200	222	0.12	11	1290	3	1.27	<2	3	55	<20



ALS Canada Ltd.
 2103 Dollarton Hwy
 North Vancouver BC V7H 0A7
 Téléphone: 604 984 0221 Télécopieur: 604 984 0218
 www.alsglobal.com

À: PAGET MINERALS CORPORATION
 1160 - 1040 W. GEORGIA ST.
 VANCOUVER BC V6E 4H1

Page: 2 - C
 Nombre total de pages: 4 (A - C)
 Finalisée date: 25-JUIL-2011
 Compte: PAGMIN

Projet: Icy Lake

CERTIFICAT D'ANALYSE TR11125472

Description échantillon	Méthode élément unités L.D.	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	Au-ICP21
		Ti %	Ti ppm	U ppm	V ppm	W ppm	Zn ppm	Au ppm
		0.01	10	10	1	10	2	0.001
L480309		0.08	<10	<10	63	70	26	0.027
L480310		0.13	<10	<10	65	60	26	0.016
L480311		0.11	<10	<10	62	50	18	0.008
L480312		0.10	<10	<10	46	60	15	0.009
L480313		0.14	<10	<10	65	40	20	0.007
L480314		0.15	<10	<10	69	50	24	0.011
L480315		0.11	<10	<10	50	<10	51	1.035
L480316		0.23	<10	<10	126	50	36	0.017
L480317		0.20	<10	<10	111	10	24	0.012
L480318		0.22	<10	<10	112	30	30	0.013
L480319		0.27	<10	<10	131	60	37	0.010
L480320		0.18	<10	<10	94	60	23	0.014
L480321		0.22	<10	<10	95	20	29	0.016
L480322		0.15	<10	<10	68	60	23	0.021
L480323		0.16	<10	<10	66	30	26	0.014
L480324		0.17	<10	<10	80	110	22	0.010
L480325		0.11	<10	<10	46	10	35	0.001
L480326		0.26	<10	<10	126	50	29	0.009
L480327		0.20	<10	<10	106	130	25	0.032
L480328		0.21	<10	<10	103	40	31	0.022
L480329		0.25	<10	<10	116	50	33	0.015
L480330		0.21	<10	<10	106	30	27	0.026
L480331		0.18	<10	<10	91	20	31	0.019
L480332		0.14	<10	<10	61	20	16	0.007
L480333		0.14	<10	<10	82	40	16	0.010
L480334		0.20	<10	<10	116	10	25	0.012
L480335		0.15	<10	<10	103	20	153	0.426
L480336		0.20	<10	<10	117	20	22	0.006
L480337		0.18	<10	<10	93	10	21	0.018
L480338		0.16	<10	<10	81	30	17	0.009
L480339		0.13	<10	<10	70	30	19	0.003
L480340		0.15	<10	<10	74	40	22	0.008
L480341		0.12	<10	<10	61	30	16	0.009
L480342		0.12	<10	<10	66	50	27	0.017
L480343		0.21	<10	<10	102	30	26	0.026
L480344		0.20	<10	<10	115	30	41	0.049
L480345		0.11	<10	<10	48	10	36	<0.001
L480346		0.21	<10	<10	123	20	49	0.040
L480347		0.15	<10	<10	128	50	39	0.025
L480348		0.17	<10	<10	79	70	25	0.022



ALS Canada Ltd.
2103 Dollarton Hwy
North Vancouver BC V7H 0A7
Téléphone: 604 984 0221 Télécopieur: 604 984 0218
www.alsglobal.com

À: PAGET MINERALS CORPORATION
1160 - 1040 W. GEORGIA ST.
VANCOUVER BC V6E 4H1

Page: 3 - A
Nombre total de pages: 4 (A -
C)
Finalisée date: 25-JUIL-2011
Compte: PAGMIN

Projet: Icy Lake

CERTIFICAT D'ANALYSE TR11125472

Description échantillon	Méthode élément unités L.D.		WEI-21	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41
	Poids reçu	Ag	Al	As	B	Ba	Be	Bi	Ca	Cd	Co	Cr	Cu	Fe	Ga	
	kg	ppm	%	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	%	ppm	
	0.02	0.2	0.01	2	10	10	0.5	2	0.01	0.5	1	1	1	0.01	10	
L480349	5.08	1.4	0.72	5	<10	30	<0.5	7	1.15	<0.5	7	11	1200	1.57	<10	
L480350	4.97	0.7	0.58	5	<10	30	<0.5	<2	1.23	<0.5	5	13	662	1.52	<10	
L480351	4.41	0.3	0.70	3	<10	20	<0.5	2	0.67	<0.5	8	11	310	1.47	<10	
L480352	5.49	0.8	0.80	11	<10	30	<0.5	3	1.51	<0.5	12	13	699	2.43	<10	
L480353	4.85	0.6	1.11	5	<10	40	<0.5	5	1.82	<0.5	11	16	621	2.93	10	
L480354	4.91	1.2	1.18	6	<10	40	<0.5	2	1.15	<0.5	12	36	1155	3.13	10	
L480355	0.07	2.0	1.56	29	<10	140	0.5	3	1.85	0.7	16	64	1860	4.10	<10	
L480356	4.95	0.5	0.98	5	<10	50	<0.5	3	0.96	<0.5	7	23	438	2.10	10	
L480357	4.40	0.6	0.68	5	<10	40	<0.5	9	0.99	<0.5	5	19	434	1.55	<10	
L480358	4.68	0.3	0.51	3	<10	40	<0.5	<2	0.87	<0.5	5	16	357	1.42	<10	
L480359	4.65	<0.2	0.53	3	<10	40	<0.5	<2	0.79	<0.5	4	11	188	1.29	<10	
L480360	4.37	<0.2	0.67	4	<10	40	<0.5	<2	0.87	<0.5	4	11	109	1.23	<10	
L480361	4.18	0.5	0.93	3	<10	20	<0.5	3	1.35	<0.5	7	20	499	1.99	<10	
L480362	4.73	0.4	1.43	8	<10	20	<0.5	<2	2.71	<0.5	10	31	479	2.51	10	
L480363	4.47	0.8	1.09	3	<10	10	<0.5	2	2.36	<0.5	12	50	986	2.51	<10	
L480364	5.28	1.4	0.84	7	<10	30	<0.5	<2	1.35	<0.5	12	41	1985	2.47	<10	
L480365	0.06	1.7	1.29	16	<10	130	<0.5	<2	0.73	<0.5	7	31	3440	3.36	<10	
L480366	3.60	1.1	0.71	4	<10	20	<0.5	5	1.78	<0.5	8	33	847	2.13	<10	
L480367	3.88	0.2	0.75	<2	<10	<10	<0.5	3	0.82	<0.5	5	17	203	1.34	<10	
L480368	1.83	0.2	0.27	2	<10	<10	<0.5	3	0.67	<0.5	3	11	201	0.88	<10	
L480369	5.16	0.8	0.63	4	<10	<10	<0.5	<2	1.29	<0.5	10	34	682	2.55	<10	
L480370	5.08	0.5	0.50	4	<10	<10	<0.5	<2	0.98	<0.5	8	28	561	1.99	<10	
L480371	4.54	0.9	0.47	6	<10	10	<0.5	3	1.23	<0.5	8	11	787	2.20	<10	
L480372	5.05	0.8	0.89	4	<10	50	<0.5	2	1.98	<0.5	11	15	540	3.07	<10	
L480373	4.66	0.3	0.76	5	<10	170	<0.5	<2	2.30	<0.5	5	8	211	1.54	<10	
L480374	4.87	<0.2	0.58	2	<10	30	<0.5	<2	0.62	<0.5	4	12	154	1.31	<10	
L480375	0.06	3.6	1.69	35	<10	110	<0.5	8	1.02	1.1	18	58	9080	4.61	<10	
L480376	4.63	0.2	0.55	2	<10	10	<0.5	<2	0.97	<0.5	5	11	266	1.41	<10	
L480377	5.35	0.6	0.90	5	<10	<10	<0.5	<2	1.48	<0.5	11	28	696	2.44	<10	
L480378	5.14	0.6	0.91	2	<10	30	<0.5	2	2.00	<0.5	10	28	544	2.51	<10	
L480379	4.42	0.7	0.85	15	<10	230	0.7	<2	4.28	<0.5	10	16	558	2.86	<10	
L480380	4.69	1.3	0.45	27	<10	400	<0.5	3	2.38	1.7	5	11	343	1.61	<10	
L480381	5.24	0.7	0.77	12	<10	150	<0.5	5	2.27	0.9	6	13	506	1.71	<10	
L480382	4.76	1.0	0.59	2	<10	20	<0.5	2	1.63	2.6	7	42	648	1.77	<10	
L480383	5.03	0.7	0.40	2	<10	<10	<0.5	3	0.75	<0.5	6	17	878	1.32	<10	
L480384	5.18	0.6	0.35	2	<10	<10	<0.5	3	0.81	<0.5	5	17	670	1.32	<10	
L480385	0.06	0.4	1.00	4	<10	50	<0.5	<2	0.65	<0.5	7	30	22	2.02	<10	
L480386	4.92	0.5	0.63	8	<10	<10	<0.5	3	0.91	<0.5	5	16	511	1.42	<10	
L480387	4.75	0.8	0.77	3	<10	20	<0.5	4	1.13	<0.5	9	41	894	2.49	<10	
L480388	4.96	0.4	0.99	3	<10	40	<0.5	11	1.05	<0.5	9	30	452	2.50	<10	



ALS Canada Ltd.
 2103 Dollarton Hwy
 North Vancouver BC V7H 0A7
 Téléphone: 604 984 0221 Télécopieur: 604 984 0218
 www.alsglobal.com

À: PAGET MINERALS CORPORATION
 1160 - 1040 W. GEORGIA ST.
 VANCOUVER BC V6E 4H1

Page: 3 - B
 Nombre total de pages: 4 (A - C)
 Finalisée date: 25-JUIL-2011
 Compte: PAGMIN

Projet: Icy Lake

CERTIFICAT D'ANALYSE TR11125472

Description échantillon	Méthode élément unités L.D.	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41
		Hg ppm 1	K % 0.01	La ppm 10	Mg % 0.01	Mn ppm 5	Mo ppm 1	Na % 0.01	Ni ppm 1	P ppm 10	Pb ppm 2	S % 0.01	Sb ppm 2	Sc ppm 1	Sr ppm 1
L480349	<1	0.14	10	0.52	149	757	0.11	6	820	3	0.69	<2	2	41	<20
L480350	<1	0.13	<10	0.41	163	452	0.06	5	470	5	0.51	<2	2	29	<20
L480351	<1	0.16	<10	0.53	135	310	0.09	6	490	5	0.58	<2	2	25	<20
L480352	<1	0.12	<10	0.59	182	85	0.08	10	1070	7	1.15	<2	4	35	<20
L480353	<1	0.17	<10	0.97	233	217	0.09	9	1280	6	0.80	<2	5	48	<20
L480354	<1	0.30	10	0.96	202	92	0.11	14	1280	5	0.80	<2	5	48	<20
L480355	<1	0.51	20	0.85	357	160	0.06	15	720	21	1.92	7	6	78	<20
L480356	<1	0.29	<10	0.87	185	185	0.10	9	670	4	0.41	<2	4	35	<20
L480357	<1	0.15	10	0.47	168	165	0.11	10	550	6	0.34	<2	3	33	<20
L480358	<1	0.11	10	0.40	139	231	0.08	5	600	5	0.34	<2	2	29	<20
L480359	<1	0.12	<10	0.40	140	124	0.08	3	420	5	0.23	<2	2	25	<20
L480360	<1	0.16	<10	0.52	160	123	0.08	4	460	4	0.14	<2	3	26	<20
L480361	<1	0.14	10	0.60	188	96	0.11	9	770	5	0.36	<2	3	38	<20
L480362	<1	0.18	10	0.96	341	165	0.14	16	1300	6	0.55	<2	6	62	<20
L480363	<1	0.13	<10	0.90	320	211	0.09	21	810	3	0.53	<2	5	42	<20
L480364	<1	0.14	10	0.75	245	162	0.11	24	1360	3	0.63	<2	3	36	<20
L480365	<1	0.11	<10	0.58	438	312	0.09	29	530	22	0.44	4	5	40	<20
L480366	<1	0.13	10	0.51	201	213	0.09	13	930	4	0.63	<2	3	33	<20
L480367	<1	0.20	<10	0.47	145	58	0.09	11	680	5	0.16	<2	3	23	<20
L480368	<1	0.14	10	0.13	96	51	0.05	5	310	7	0.27	<2	1	14	20
L480369	<1	0.13	<10	0.57	212	87	0.09	16	1260	5	0.59	<2	3	27	<20
L480370	<1	0.13	10	0.35	147	93	0.09	11	1130	4	0.33	<2	2	23	<20
L480371	<1	0.12	10	0.40	185	800	0.09	8	1330	5	0.73	<2	2	29	<20
L480372	<1	0.26	10	0.90	341	147	0.07	11	1130	3	0.89	<2	5	35	<20
L480373	<1	0.23	<10	0.52	260	176	0.04	5	510	3	0.32	<2	3	49	<20
L480374	<1	0.22	<10	0.39	128	77	0.10	4	530	3	0.15	<2	2	23	<20
L480375	<1	0.53	10	1.05	520	880	0.11	35	870	40	2.06	7	9	48	<20
L480376	<1	0.18	<10	0.39	145	58	0.08	6	720	3	0.25	<2	2	23	<20
L480377	<1	0.18	<10	0.64	193	154	0.13	17	1210	7	0.50	<2	4	36	<20
L480378	<1	0.24	10	0.78	284	90	0.09	14	1250	3	0.42	<2	5	295	<20
L480379	<1	0.30	10	1.23	569	231	0.06	11	1600	4	0.34	6	8	157	<20
L480380	<1	0.21	<10	0.66	529	197	0.04	7	620	73	0.46	14	4	147	<20
L480381	<1	0.22	<10	0.66	373	231	0.06	8	580	28	0.47	5	4	140	<20
L480382	<1	0.17	<10	0.68	282	160	0.06	11	770	14	0.46	<2	4	48	<20
L480383	<1	0.12	<10	0.28	109	192	0.08	7	530	4	0.41	<2	1	25	<20
L480384	<1	0.11	<10	0.25	108	224	0.07	6	610	4	0.32	<2	1	21	<20
L480385	<1	0.06	<10	0.49	306	4	0.05	21	490	3	0.02	<2	4	29	<20
L480386	<1	0.19	<10	0.39	131	196	0.10	8	670	4	0.25	<2	2	21	<20
L480387	<1	0.32	<10	0.66	176	312	0.10	13	940	2	0.49	<2	4	24	<20
L480388	<1	0.53	<10	0.85	231	126	0.12	14	1100	3	0.31	<2	5	23	<20



ALS Canada Ltd.
 2103 Dollarton Hwy
 North Vancouver BC V7H 0A7
 Téléphone: 604 984 0221 Télécopieur: 604 984 0218
 www.alsglobal.com

À: PAGET MINERALS CORPORATION
 1160 - 1040 W. GEORGIA ST.
 VANCOUVER BC V6E 4H1

Page: 3 - C
 Nombre total de pages: 4 (A - C)
 Finalisée date: 25-JUIL-2011
 Compte: PAGMIN

Projet: Icy Lake

CERTIFICAT D'ANALYSE TR11125472

Description échantillon	Méthode élément unités L.D.	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	Au-ICP21
		Ti %	Ti ppm	U ppm	V ppm	W ppm	Zn ppm	Au ppm
		0.01	10	10	1	10	2	0.001
L480349		0.13	<10	<10	54	30	17	0.031
L480350		0.06	<10	<10	42	20	17	0.006
L480351		0.10	<10	<10	43	10	16	0.005
L480352		0.15	<10	<10	71	10	41	0.009
L480353		0.22	<10	<10	104	10	31	0.009
L480354		0.25	<10	<10	132	10	31	0.024
L480355		0.04	<10	<10	57	<10	67	0.215
L480356		0.17	<10	<10	84	10	26	0.006
L480357		0.11	<10	<10	53	10	18	0.009
L480358		0.10	<10	<10	49	10	15	0.003
L480359		0.08	<10	<10	39	10	14	0.004
L480360		0.08	<10	<10	43	10	16	<0.001
L480361		0.12	<10	<10	69	20	19	0.010
L480362		0.16	<10	<10	110	20	29	0.008
L480363		0.12	<10	<10	88	20	29	0.010
L480364		0.18	<10	<10	83	30	35	0.016
L480365		0.12	<10	<10	54	<10	52	0.961
L480366		0.14	<10	<10	66	50	18	0.008
L480367		0.12	<10	<10	55	10	17	0.001
L480368		0.05	<10	10	21	10	8	0.002
L480369		0.18	<10	<10	101	10	22	0.009
L480370		0.16	<10	<10	79	20	19	0.016
L480371		0.16	<10	<10	73	30	19	0.009
L480372		0.15	<10	<10	99	10	35	0.004
L480373		0.03	<10	<10	34	10	20	0.001
L480374		0.11	<10	<10	47	20	13	0.001
L480375		0.15	<10	<10	100	20	157	0.698
L480376		0.11	<10	<10	48	20	13	0.002
L480377		0.17	<10	<10	96	30	18	0.009
L480378		0.15	<10	<10	94	10	24	0.005
L480379		0.03	<10	<10	64	10	43	0.010
L480380		0.01	<10	<10	27	10	76	0.008
L480381		0.04	<10	<10	38	10	51	0.006
L480382		0.08	<10	<10	51	20	138	0.010
L480383		0.09	<10	<10	38	30	13	0.007
L480384		0.10	<10	<10	41	10	12	0.007
L480385		0.11	<10	<10	45	10	34	0.003
L480386		0.13	<10	<10	49	10	13	0.006
L480387		0.19	<10	<10	100	20	24	0.013
L480388		0.24	<10	<10	106	20	26	0.006



ALS Canada Ltd.
 2103 Dollarton Hwy
 North Vancouver BC V7H 0A7
 Téléphone: 604 984 0221 Télécopieur: 604 984 0218
 www.alsglobal.com

À: PAGET MINERALS CORPORATION
 1160 - 1040 W. GEORGIA ST.
 VANCOUVER BC V6E 4H1

Page: 4 - A
 Nombre total de pages: 4 (A - C)
 Finalisée date: 25-JUIL-2011
 Compte: PAGMIN

Projet: Icy Lake

CERTIFICAT D'ANALYSE TR11125472

Description échantillon	Méthode élément unités L.D.	WEI-21	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	
		Poids reçu kg	Ag ppm	Al %	As ppm	B ppm	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	Ga ppm
		0.02	0.2	0.01	2	10	10	0.5	2	0.01	0.5	1	1	1	0.01	10
L480389		5.33	0.5	1.03	4	<10	20	<0.5	<2	1.28	<0.5	11	43	559	2.87	<10
L480390		4.62	0.9	0.76	5	<10	30	<0.5	<2	1.30	<0.5	9	20	891	2.49	<10
L480391		5.23	0.5	1.02	3	<10	50	<0.5	2	1.29	<0.5	8	59	569	2.58	<10



ALS Canada Ltd.
 2103 Dollarton Hwy
 North Vancouver BC V7H 0A7
 Téléphone: 604 984 0221 Télécopieur: 604 984 0218
 www.alsglobal.com

À: PAGET MINERALS CORPORATION
 1160 - 1040 W. GEORGIA ST.
 VANCOUVER BC V6E 4H1

Page: 4 - B
 Nombre total de pages: 4 (A - C)
 Finalisée date: 25-JUIL-2011
 Compte: PAGMIN

Projet: Icy Lake

CERTIFICAT D'ANALYSE TR11125472

Description échantillon	Méthode élément unités L.D.	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41
		Hg ppm	K %	La ppm	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	S %	Sb ppm	Sc ppm	Sr ppm	Th ppm
		1	0.01	10	0.01	5	1	0.01	1	10	2	0.01	2	1	1	20
L480389		<1	0.41	<10	0.73	240	61	0.12	16	1970	2	0.42	<2	4	31	<20
L480390		<1	0.27	10	0.65	194	344	0.12	14	1660	3	0.51	<2	4	97	<20
L480391		<1	0.29	<10	0.78	204	223	0.15	28	1070	3	0.39	<2	4	97	<20



ALS Canada Ltd.
 2103 Dollarton Hwy
 North Vancouver BC V7H 0A7
 Téléphone: 604 984 0221 Télécopieur: 604 984 0218
 www.alsglobal.com

À: PAGET MINERALS CORPORATION
 1160 - 1040 W. GEORGIA ST.
 VANCOUVER BC V6E 4H1

Page: 4 - C
 Nombre total de pages: 4 (A - C)
 Finalisée date: 25-JUIL-2011
 Compte: PAGMIN

Projet: Icy Lake

CERTIFICAT D'ANALYSE TR11125472

Description échantillon	Méthode élément unités L.D.	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	Au-ICP21
		Ti %	Ti ppm	U ppm	V ppm	W ppm	Zn ppm	Au ppm
		0.01	10	10	1	10	2	0.001
L480389		0.23	<10	<10	121	10	26	0.006
L480390		0.21	<10	<10	98	50	22	0.015
L480391		0.17	<10	<10	99	10	23	0.011



ALS Canada Ltd.
2103 Dollarton Hwy
North Vancouver BC V7H 0A7
Téléphone: 604 984 0221 Télécopieur: 604 984 0218
www.alsglobal.com

À: PAGET MINERALS CORPORATION
1160 - 1040 W. GEORGIA ST.
VANCOUVER BC V6E 4H1

Page: 1
Finalisée date: 9-AOUT-2011
Cette copie a fait un rapport sur
9-NOV-2011
Compte: PAGMIN

CERTIFICAT TR11126835

Projet: Icy Lake

Bon de commande #:

Ce rapport s'applique aux 98 échantillons de carotte forage soumis à notre laboratoire de Terrace, BC, Canada le 13-JUIL-2011.

Les résultats sont transmis à:

SONIA JEYACHANDRAN

ROD OGILVIE

DAVID VOLKERT

PRÉPARATION ÉCHANTILLONS

CODE ALS	DESCRIPTION
WEI-21	Poids échantillon reçu
LOG-22	Entrée échantillon - Reçu sans code barre
CRU-QC	Test concassage QC
PUL-QC	Test concassage QC
CRU-31	Granulation - 70 % <2 mm
SPL-21	Échant. fractionné - div. riffles
PUL-31	Pulvérisé à 85 % <75 um
LOG-23	Entrée pulpe - Reçu avec code barre

PROCÉDURES ANALYTIQUES

CODE ALS	DESCRIPTION	INSTRUMENT
Au-ICP21	Au 30 g FA fini ICP-AES	ICP-AES
ME-ICP41	Aqua regia ICP-AES 35 éléments	ICP-AES

À: PAGET MINERALS CORPORATION
ATTN: DAVID VOLKERT
1160 - 1040 W. GEORGIA ST.
VANCOUVER BC V6E 4H1

Ce rapport est final et remplace tout autre rapport préliminaire portant ce numéro de certificat. Les résultats s'appliquent aux échantillons soumis. Toutes les pages de ce rapport ont été vérifiées et approuvées avant publication.

Signature:



Colin Ramshaw, Vancouver Laboratory Manager



ALS Canada Ltd.
 2103 Dollarton Hwy
 North Vancouver BC V7H 0A7
 Téléphone: 604 984 0221 Télécopieur: 604 984 0218
 www.alsglobal.com

À: PAGET MINERALS CORPORATION
 1160 - 1040 W. GEORGIA ST.
 VANCOUVER BC V6E 4H1

Page: 2 - A
 Nombre total de pages: 4 (A - C)
 Finalisée date: 9-AOUT-2011
 Compte: PAGMIN

Projet: Icy Lake

CERTIFICAT D'ANALYSE TR11126835

Description échantillon	Méthode élément unités L.D.	WEI-21	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41
		Poids reçu kg	Ag ppm	Al %	As ppm	B ppm	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	Ga ppm
L480392		4.77	0.5	0.63	4	<10	40	<0.5	5	1.55	<0.5	5	12	423	1.54	<10
L480393		4.84	0.6	0.63	3	<10	60	<0.5	5	1.00	<0.5	6	7	569	1.87	<10
L480394		4.59	0.9	0.75	5	<10	120	<0.5	7	2.73	<0.5	6	14	831	1.90	<10
L480395		0.06	2.1	1.48	30	<10	150	<0.5	3	1.83	0.8	16	62	1825	3.99	<10
L480396		5.03	2.0	0.55	10	<10	300	0.6	19	3.57	0.7	9	10	1065	2.18	<10
L480397		5.03	1.1	0.61	3	<10	250	0.5	4	2.85	<0.5	10	7	1195	2.09	<10
L480398		4.43	1.8	0.54	7	<10	580	0.5	<2	3.29	<0.5	6	9	1155	1.94	<10
L480399		5.32	2.7	0.36	25	<10	370	<0.5	<2	3.69	1.1	8	3	367	1.83	<10
L480400		4.96	1.2	0.39	8	<10	270	<0.5	3	2.74	<0.5	6	3	455	1.64	<10
L480401		4.24	0.6	0.40	6	<10	380	0.5	<2	2.71	<0.5	5	8	495	1.60	<10
L480402		4.78	0.4	0.38	6	<10	290	<0.5	2	2.89	<0.5	5	5	301	1.42	<10
L480403		4.52	0.8	0.65	5	<10	140	<0.5	6	3.04	<0.5	7	10	415	1.82	<10
L480404		3.97	0.6	0.67	3	<10	90	<0.5	<2	2.06	<0.5	6	10	300	1.70	<10
L480405		0.06	0.2	0.99	2	<10	70	<0.5	<2	0.62	<0.5	6	30	21	1.96	<10
L480406		5.11	0.6	0.81	2	<10	160	<0.5	<2	1.19	<0.5	6	36	314	1.89	<10
L480407		5.21	1.0	0.98	8	<10	80	0.6	<2	3.68	<0.5	9	36	491	2.43	<10
L480408		4.77	0.6	1.25	9	<10	90	0.8	2	4.17	<0.5	10	14	403	2.60	<10
L480409		5.05	0.6	0.62	5	<10	140	0.5	3	2.81	<0.5	7	7	622	1.94	<10
L480410		5.00	0.8	0.55	4	<10	160	<0.5	3	1.62	<0.5	8	9	708	1.89	<10
L480411		5.31	0.4	0.52	6	<10	70	<0.5	<2	1.06	<0.5	5	28	349	1.36	<10
L480412		4.57	0.5	0.44	3	<10	40	<0.5	9	0.83	<0.5	6	14	668	1.37	<10
L480413		4.19	0.2	0.48	3	<10	30	<0.5	8	0.96	<0.5	7	12	412	1.64	<10
L480414		4.88	0.6	0.44	2	<10	40	<0.5	6	1.18	<0.5	7	10	919	1.54	<10
L480415		0.06	1.7	1.34	13	<10	130	<0.5	3	0.74	<0.5	9	33	3540	3.39	<10
L480416		4.93	0.6	0.53	3	<10	40	<0.5	32	0.97	<0.5	7	14	789	1.47	<10
L480417		4.37	0.4	0.41	<2	<10	100	<0.5	11	1.13	<0.5	5	15	504	1.34	<10
L480418		5.00	2.3	0.60	36	<10	60	<0.5	40	2.10	1.3	8	16	1175	1.64	<10
L480419		4.65	1.0	0.92	5	<10	90	<0.5	10	2.53	<0.5	10	19	639	2.33	<10
L480420		4.63	0.5	0.81	6	<10	330	<0.5	4	1.98	<0.5	12	29	783	2.45	<10
L480421		4.65	0.2	0.46	4	<10	40	<0.5	2	0.81	<0.5	8	26	406	1.54	<10
L480422		4.92	2.4	0.52	6	<10	60	<0.5	7	0.97	1.0	26	23	2080	2.57	<10
L480423		5.44	0.9	0.45	18	<10	50	<0.5	4	1.27	1.3	7	25	536	1.26	<10
L480424		4.63	0.4	0.39	2	<10	40	<0.5	4	0.97	<0.5	6	19	521	1.31	<10
L480425		0.06	<0.2	1.08	4	<10	80	<0.5	<2	0.67	<0.5	7	30	23	2.07	<10
L480426		5.06	0.5	0.40	<2	<10	40	<0.5	4	0.80	<0.5	6	25	539	1.17	<10
L480427		5.17	0.6	0.46	4	<10	30	<0.5	3	0.97	<0.5	7	20	691	1.38	<10
L480428		4.23	<0.2	0.37	<2	<10	30	<0.5	3	0.71	<0.5	4	25	224	0.97	<10
L480429		4.95	0.2	0.40	<2	<10	160	<0.5	3	1.29	<0.5	5	20	310	1.18	<10
L480430		4.85	0.2	0.61	5	<10	60	<0.5	6	1.63	<0.5	7	30	369	1.65	<10
L480431		4.88	0.2	0.47	5	<10	40	<0.5	4	0.70	<0.5	6	30	333	1.42	<10



ALS Canada Ltd.
 2103 Dollarton Hwy
 North Vancouver BC V7H 0A7
 Téléphone: 604 984 0221 Télécopieur: 604 984 0218
 www.alsglobal.com

À: PAGET MINERALS CORPORATION
 1160 - 1040 W. GEORGIA ST.
 VANCOUVER BC V6E 4H1

Page: 2 - B
 Nombre total de pages: 4 (A - C)
 Finalisée date: 9-AOUT-2011
 Compte: PAGMIN

Projet: Icy Lake

CERTIFICAT D'ANALYSE TR11126835

Description échantillon	Méthode élément unités L.D.	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	
		Hg ppm	K %	La ppm	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	S %	Sb ppm	Sc ppm	Sr ppm	Th ppm
		1	0.01	10	0.01	5	1	0.01	1	10	2	0.01	2	1	1	20
L480392		<1	0.15	10	0.68	239	448	0.07	5	1050	3	0.32	<2	3	52	<20
L480393		<1	0.19	10	0.84	149	389	0.09	5	1330	3	0.39	<2	3	61	<20
L480394		<1	0.13	10	0.75	329	353	0.04	5	910	5	0.44	<2	5	101	<20
L480395		<1	0.50	20	0.83	345	157	0.05	15	690	19	1.82	7	6	72	<20
L480396		<1	0.23	10	0.75	422	84	0.03	6	830	8	0.67	9	6	427	<20
L480397		<1	0.20	10	0.64	305	382	0.04	8	1700	3	0.55	<2	5	125	<20
L480398		<1	0.25	10	0.83	366	86	0.03	7	810	4	0.48	4	7	372	<20
L480399		<1	0.23	10	0.88	664	153	0.01	5	600	15	0.78	25	4	150	<20
L480400		<1	0.22	10	0.74	547	459	0.02	3	790	11	0.76	3	3	91	<20
L480401		<1	0.21	10	0.79	373	43	0.02	5	670	4	0.45	3	4	118	<20
L480402		<1	0.21	10	0.69	529	239	0.02	3	570	5	0.40	2	4	115	<20
L480403		<1	0.18	10	0.68	444	127	0.02	5	730	12	0.52	3	4	78	<20
L480404		<1	0.15	10	0.66	264	494	0.05	5	590	4	0.39	<2	3	256	<20
L480405		<1	0.06	<10	0.47	293	3	0.04	18	470	<2	0.05	<2	4	28	<20
L480406		<1	0.23	10	1.01	211	53	0.07	7	760	2	0.29	<2	4	342	<20
L480407		<1	0.19	10	1.08	456	232	0.05	9	1670	11	0.77	2	7	121	<20
L480408		<1	0.22	20	0.86	463	205	0.03	15	1710	10	0.75	2	9	137	<20
L480409		<1	0.20	20	0.66	317	165	0.04	6	1560	6	0.47	<2	5	100	<20
L480410		<1	0.16	10	0.63	215	164	0.07	7	1300	5	0.53	2	3	89	<20
L480411		<1	0.19	10	0.68	154	200	0.08	7	720	5	0.22	4	2	86	<20
L480412		<1	0.16	10	0.51	123	137	0.08	7	910	5	0.27	<2	2	36	<20
L480413		<1	0.15	10	0.44	133	45	0.09	6	900	4	0.32	<2	2	35	<20
L480414		<1	0.13	10	0.41	165	112	0.07	6	730	5	0.27	<2	2	44	<20
L480415		<1	0.11	10	0.58	456	312	0.10	29	540	21	0.44	4	5	40	<20
L480416		<1	0.17	10	0.51	138	329	0.09	6	860	6	0.31	<2	2	51	<20
L480417		<1	0.13	10	0.29	169	29	0.06	5	440	7	0.19	<2	2	38	<20
L480418		<1	0.17	10	0.53	282	199	0.05	8	820	42	0.53	40	4	69	<20
L480419		<1	0.15	10	0.77	392	96	0.05	9	770	13	0.57	4	5	107	<20
L480420		<1	0.35	10	0.92	278	148	0.07	17	1640	3	0.57	2	3	80	<20
L480421		<1	0.19	10	0.39	105	125	0.08	12	900	4	0.35	<2	2	32	<20
L480422		<1	0.14	<10	0.43	163	380	0.07	13	740	30	1.04	<2	2	30	<20
L480423		<1	0.15	<10	0.37	179	400	0.07	10	730	87	0.29	17	2	30	<20
L480424		<1	0.13	10	0.24	95	48	0.08	10	820	5	0.28	2	1	27	<20
L480425		<1	0.07	<10	0.48	315	4	0.06	20	500	<2	0.05	<2	4	31	<20
L480426		<1	0.15	10	0.29	99	47	0.08	10	750	6	0.25	<2	1	25	<20
L480427		<1	0.15	10	0.30	111	247	0.09	12	820	5	0.33	<2	2	29	<20
L480428		<1	0.14	<10	0.28	89	430	0.08	8	710	5	0.21	<2	1	23	<20
L480429		<1	0.10	10	0.43	170	83	0.07	9	600	4	0.25	<2	2	42	<20
L480430		<1	0.18	10	0.52	186	65	0.07	13	730	4	0.22	6	3	35	<20
L480431		<1	0.20	<10	0.37	105	44	0.10	11	770	3	0.22	<2	2	25	<20



ALS Canada Ltd.
 2103 Dollarton Hwy
 North Vancouver BC V7H 0A7
 Téléphone: 604 984 0221 Télécopieur: 604 984 0218
 www.alsglobal.com

À: PAGET MINERALS CORPORATION
 1160 - 1040 W. GEORGIA ST.
 VANCOUVER BC V6E 4H1

Page: 2 - C
 Nombre total de pages: 4 (A - C)
 Finalisée date: 9-AOUT-2011
 Compte: PAGMIN

Projet: Icy Lake

CERTIFICAT D'ANALYSE TR11126835

Description échantillon	Méthode élément unités L.D.	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	Au-ICP21
		Ti %	Ti ppm	U ppm	V ppm	W ppm	Zn ppm	Au ppm
		0.01	10	10	1	10	2	0.001
L480392		0.11	<10	<10	61	40	16	0.006
L480393		0.14	<10	<10	76	40	17	0.011
L480394		0.06	<10	<10	64	20	26	0.006
L480395		0.04	<10	<10	56	<10	63	0.212
L480396		0.01	<10	<10	42	20	37	0.015
L480397		0.04	<10	<10	49	20	22	0.018
L480398		0.01	<10	<10	43	10	25	0.011
L480399		<0.01	<10	<10	16	<10	42	0.014
L480400		<0.01	<10	<10	12	<10	19	0.010
L480401		<0.01	<10	<10	21	<10	19	0.005
L480402		<0.01	<10	<10	18	<10	23	0.006
L480403		0.03	<10	10	43	10	28	0.014
L480404		0.06	<10	<10	53	10	17	0.008
L480405		0.10	<10	<10	44	10	33	0.001
L480406		0.10	<10	<10	64	<10	20	0.008
L480407		0.08	<10	<10	72	<10	33	0.008
L480408		0.01	<10	<10	60	<10	37	0.007
L480409		0.08	<10	<10	44	10	24	0.015
L480410		0.13	<10	<10	52	140	19	0.016
L480411		0.11	<10	<10	55	<10	16	0.009
L480412		0.12	<10	<10	57	10	13	0.010
L480413		0.14	<10	<10	62	<10	13	0.010
L480414		0.10	<10	<10	52	20	17	0.015
L480415		0.12	<10	<10	55	<10	55	1.095
L480416		0.13	<10	<10	57	20	14	0.013
L480417		0.05	<10	<10	37	20	14	0.006
L480418		0.07	<10	<10	51	30	61	0.056
L480419		0.04	<10	<10	65	10	31	0.012
L480420		0.18	<10	<10	91	<10	27	0.014
L480421		0.13	<10	<10	55	<10	14	0.011
L480422		0.11	<10	<10	54	10	84	0.028
L480423		0.11	<10	<10	46	<10	70	0.019
L480424		0.12	<10	<10	49	<10	14	0.014
L480425		0.11	<10	<10	46	10	34	0.002
L480426		0.13	<10	<10	47	10	17	0.016
L480427		0.13	<10	<10	53	10	19	0.020
L480428		0.12	<10	<10	42	<10	11	0.010
L480429		0.09	<10	<10	45	10	12	0.006
L480430		0.10	<10	<10	61	10	19	0.010
L480431		0.14	<10	<10	58	<10	14	0.008



ALS Canada Ltd.
 2103 Dollarton Hwy
 North Vancouver BC V7H 0A7
 Téléphone: 604 984 0221 Télécopieur: 604 984 0218
 www.alsglobal.com

À: PAGET MINERALS CORPORATION
 1160 - 1040 W. GEORGIA ST.
 VANCOUVER BC V6E 4H1

Page: 3 - A
 Nombre total de pages: 4 (A - C)
 Finalisée date: 9-AOUT-2011
 Compte: PAGMIN

Projet: Icy Lake

CERTIFICAT D'ANALYSE TR11126835

Description échantillon	Méthode élément unités L.D.	WEI-21	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41
		Poids reçu kg	Ag ppm	Al %	As ppm	B ppm	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	Ga ppm
		0.02	0.2	0.01	2	10	10	0.5	2	0.01	0.5	1	1	1	0.01	10
L480432		4.64	<0.2	0.50	<2	<10	50	<0.5	3	0.92	<0.5	5	26	203	1.15	<10
L480433		4.75	0.5	0.90	31	<10	300	<0.5	3	2.71	0.6	8	26	339	1.98	<10
L480434		4.40	0.2	0.55	3	<10	60	<0.5	7	1.06	<0.5	7	31	262	1.59	<10
L480435		0.06	3.8	1.89	36	<10	130	<0.5	9	1.04	0.9	19	61	9630	4.73	10
L480436		4.72	<0.2	0.44	2	<10	40	<0.5	3	1.18	<0.5	6	26	267	1.28	<10
L480437		5.03	<0.2	0.52	<2	<10	80	<0.5	4	1.51	<0.5	5	26	148	1.02	<10
L480438		4.93	0.2	0.48	<2	<10	40	<0.5	4	1.21	<0.5	6	28	238	1.35	<10
L480439		4.66	0.3	0.51	<2	<10	40	<0.5	3	1.33	<0.5	6	30	302	1.40	<10
L480440		4.87	0.3	0.43	2	<10	40	<0.5	5	0.97	<0.5	6	23	392	1.19	<10
L480441		4.54	0.5	0.36	<2	<10	50	<0.5	10	1.11	<0.5	5	19	432	0.96	<10
L480442		4.54	0.3	0.31	<2	<10	60	<0.5	6	0.75	<0.5	4	17	271	0.85	<10
L480443		4.69	0.4	0.46	<2	<10	30	<0.5	6	1.70	<0.5	4	19	319	1.02	<10
L480444		4.61	1.3	0.57	12	<10	110	<0.5	20	2.51	<0.5	6	21	698	1.37	<10
L480445		0.06	<0.2	1.10	3	<10	80	<0.5	<2	0.68	<0.5	7	30	22	2.07	<10
L480446		4.84	0.3	0.33	<2	<10	60	<0.5	6	0.98	<0.5	4	18	414	0.77	<10
L480447		5.00	0.3	0.29	<2	<10	50	<0.5	21	0.94	<0.5	3	13	399	0.63	<10
L480448		5.26	0.4	0.29	3	<10	60	<0.5	5	1.05	<0.5	3	19	371	0.84	<10
L480449		5.03	0.3	0.39	<2	<10	100	<0.5	3	1.10	<0.5	3	16	262	1.11	<10
L480450		4.68	0.9	0.47	2	<10	130	<0.5	79	2.36	<0.5	6	25	765	1.45	<10
L480451		4.38	0.5	0.46	2	<10	60	<0.5	9	1.63	<0.5	4	19	461	1.16	<10
L480452		5.02	0.4	0.38	<2	<10	60	<0.5	24	1.17	<0.5	4	19	534	0.96	<10
L480453		4.65	1.4	0.43	2	<10	80	<0.5	22	1.15	<0.5	5	18	1425	1.39	<10
L480454		5.02	4.1	0.79	<2	<10	130	<0.5	24	3.36	<0.5	6	21	367	1.81	<10
L480455		0.06	2.1	1.58	30	<10	140	0.5	4	1.93	1.0	17	66	1875	4.10	<10
L480456		4.25	1.0	0.77	2	<10	200	<0.5	6	3.65	<0.5	6	18	556	1.69	<10
L480457		4.44	0.4	0.74	2	<10	140	<0.5	2	3.52	<0.5	5	39	394	1.84	<10
L480458		4.47	<0.2	0.45	<2	<10	80	<0.5	6	1.09	<0.5	5	58	180	1.74	<10
L480459		4.70	0.2	0.44	<2	<10	110	<0.5	<2	1.02	<0.5	4	46	329	1.33	<10
L480460		4.20	0.3	0.40	<2	<10	80	<0.5	6	0.98	<0.5	3	27	336	1.42	<10
L480461		5.28	1.4	0.58	<2	<10	100	<0.5	6	1.36	<0.5	5	18	671	1.70	<10
L480462		4.31	1.5	0.78	17	<10	430	<0.5	8	2.78	0.5	8	9	874	2.19	<10
L480463		4.79	1.0	0.55	16	<10	350	<0.5	11	2.46	<0.5	6	18	851	1.53	<10
L480464		5.20	1.1	0.46	4	<10	100	<0.5	29	1.66	<0.5	7	11	1040	2.21	<10
L480465		0.06	0.2	1.02	4	<10	80	<0.5	<2	0.66	<0.5	7	30	22	1.94	<10
L480466		4.81	0.8	0.30	3	<10	120	<0.5	16	0.93	<0.5	7	21	822	1.45	<10
L480467		4.45	0.5	0.32	3	<10	100	<0.5	5	0.86	<0.5	5	18	505	1.08	<10
L480468		4.88	0.4	0.26	2	<10	80	<0.5	5	0.78	<0.5	4	14	405	1.26	<10
L480469		4.97	0.4	0.31	3	<10	100	<0.5	3	0.96	<0.5	4	10	421	1.14	<10
L480470		4.49	0.5	0.37	<2	<10	200	<0.5	17	1.30	<0.5	6	6	675	1.61	<10
L480471		5.15	0.3	0.33	3	<10	150	<0.5	5	1.06	<0.5	4	7	355	0.71	<10



ALS Canada Ltd.
 2103 Dollarton Hwy
 North Vancouver BC V7H 0A7
 Téléphone: 604 984 0221 Télécopieur: 604 984 0218
 www.alsglobal.com

À: PAGET MINERALS CORPORATION
 1160 - 1040 W. GEORGIA ST.
 VANCOUVER BC V6E 4H1

Page: 3 - B
 Nombre total de pages: 4 (A - C)
 Finalisée date: 9-AOUT-2011
 Compte: PAGMIN

Projet: Icy Lake

CERTIFICAT D'ANALYSE TR11126835

Description échantillon	Méthode élément unités L.D.	ME-ICP41 Hg ppm 1	ME-ICP41 K % 0.01	ME-ICP41 La ppm 10	ME-ICP41 Mg % 0.01	ME-ICP41 Mn ppm 5	ME-ICP41 Mo ppm 1	ME-ICP41 Na % 0.01	ME-ICP41 Ni ppm 1	ME-ICP41 P ppm 10	ME-ICP41 Pb ppm 2	ME-ICP41 S % 0.01	ME-ICP41 Sb ppm 2	ME-ICP41 Sc ppm 1	ME-ICP41 Sr ppm 1	ME-ICP41 Th ppm 20
L480432		<1	0.19	10	0.59	152	60	0.08	9	640	4	0.18	<2	2	28	<20
L480433		<1	0.25	10	0.70	290	148	0.06	13	660	32	0.33	5	5	67	<20
L480434		<1	0.20	10	0.61	172	208	0.07	13	900	17	0.25	2	2	30	<20
L480435		<1	0.56	10	1.06	542	951	0.12	36	920	40	2.22	5	10	51	<20
L480436		<1	0.14	10	0.40	162	55	0.08	9	580	16	0.20	<2	2	33	<20
L480437		<1	0.11	10	0.54	169	138	0.09	9	730	5	0.14	<2	3	71	<20
L480438		<1	0.13	10	0.47	159	74	0.08	10	690	4	0.16	<2	2	38	<20
L480439		<1	0.11	10	0.41	155	125	0.06	11	650	2	0.23	<2	3	49	<20
L480440		<1	0.14	<10	0.37	121	109	0.08	10	640	4	0.25	<2	2	30	<20
L480441		<1	0.10	<10	0.29	125	272	0.06	7	640	4	0.29	<2	2	41	<20
L480442		<1	0.12	10	0.29	98	60	0.08	6	730	4	0.20	<2	1	31	<20
L480443		<1	0.09	10	0.48	224	69	0.06	8	660	4	0.20	<2	3	48	<20
L480444		<1	0.12	<10	0.62	297	268	0.05	9	670	12	0.59	7	4	69	<20
L480445		<1	0.07	<10	0.48	317	4	0.06	20	500	2	0.05	<2	4	32	<20
L480446		<1	0.11	10	0.41	120	45	0.07	6	770	4	0.21	<2	1	37	<20
L480447		<1	0.10	10	0.21	90	54	0.08	4	860	5	0.18	<2	1	36	<20
L480448		<1	0.10	10	0.27	100	52	0.07	6	890	5	0.26	<2	1	47	<20
L480449		<1	0.10	10	0.49	163	183	0.09	4	840	8	0.22	<2	2	55	<20
L480450		<1	0.09	10	0.52	259	179	0.06	8	870	8	0.55	<2	4	123	<20
L480451		<1	0.10	10	0.65	170	72	0.08	8	950	6	0.26	<2	3	70	<20
L480452		<1	0.09	10	0.56	133	195	0.08	7	880	7	0.37	<2	2	77	<20
L480453		<1	0.11	10	0.64	159	116	0.08	7	810	8	0.45	<2	2	69	<20
L480454		<1	0.12	10	0.94	395	106	0.06	9	730	178	0.58	<2	6	99	<20
L480455		1	0.53	20	0.85	366	159	0.07	17	690	23	1.91	7	6	75	<20
L480456		<1	0.12	10	0.84	408	252	0.06	9	730	11	0.54	<2	6	133	<20
L480457		<1	0.16	10	0.70	338	183	0.05	14	820	4	0.24	<2	6	153	<20
L480458		<1	0.14	10	0.68	119	56	0.09	15	850	4	0.25	<2	2	78	<20
L480459		<1	0.16	10	0.68	128	166	0.08	10	870	3	0.20	<2	2	89	<20
L480460		<1	0.10	10	0.54	135	328	0.09	5	810	5	0.17	<2	2	64	<20
L480461		<1	0.10	10	0.79	234	963	0.08	6	860	123	0.42	<2	4	92	<20
L480462		<1	0.14	10	0.56	326	109	0.05	6	770	18	0.71	17	5	302	<20
L480463		<1	0.10	10	0.34	251	77	0.06	5	720	7	0.38	20	3	151	<20
L480464		<1	0.09	20	0.37	189	112	0.09	6	1070	6	0.66	<2	2	86	<20
L480465		1	0.06	<10	0.47	301	4	0.06	20	470	2	0.05	<2	4	30	<20
L480466		<1	0.07	10	0.29	104	45	0.08	7	890	7	0.60	<2	1	52	<20
L480467		<1	0.09	10	0.23	86	59	0.10	5	870	6	0.44	<2	1	50	<20
L480468		<1	0.07	10	0.17	96	107	0.08	4	780	6	0.51	<2	1	46	<20
L480469		<1	0.09	10	0.27	123	56	0.09	4	780	5	0.36	<2	1	55	<20
L480470		<1	0.08	10	0.33	137	32	0.08	4	1120	6	0.63	<2	2	157	<20
L480471		<1	0.09	10	0.34	104	56	0.09	4	820	5	0.25	<2	1	68	<20



ALS Canada Ltd.
 2103 Dollarton Hwy
 North Vancouver BC V7H 0A7
 Téléphone: 604 984 0221 Télécopieur: 604 984 0218
 www.alsglobal.com

À: PAGET MINERALS CORPORATION
 1160 - 1040 W. GEORGIA ST.
 VANCOUVER BC V6E 4H1

Page: 3 - C
 Nombre total de pages: 4 (A - C)
 Finalisée date: 9-AOUT-2011
 Compte: PAGMIN

Projet: Icy Lake

CERTIFICAT D'ANALYSE TR11126835

Description échantillon	Méthode élément unités L.D.	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	Au-ICP21
		Ti %	Ti ppm	U ppm	V ppm	W ppm	Zn ppm	Au ppm
		0.01	10	10	1	10	2	0.001
L480432		0.11	<10	<10	49	<10	13	0.004
L480433		0.06	<10	<10	55	<10	47	0.005
L480434		0.12	<10	<10	55	10	36	0.010
L480435		0.16	<10	<10	108	20	161	0.719
L480436		0.11	<10	<10	49	10	33	0.005
L480437		0.11	<10	<10	49	10	15	0.005
L480438		0.12	<10	<10	55	<10	16	0.006
L480439		0.09	<10	<10	53	10	15	0.007
L480440		0.11	<10	<10	45	10	13	0.006
L480441		0.08	<10	<10	35	10	11	0.007
L480442		0.10	<10	<10	32	20	9	0.003
L480443		0.08	<10	<10	40	10	14	0.005
L480444		0.07	<10	<10	44	20	26	0.005
L480445		0.12	<10	<10	47	10	34	0.002
L480446		0.11	<10	<10	34	20	10	0.003
L480447		0.12	<10	<10	32	20	7	0.005
L480448		0.11	<10	<10	37	50	13	0.004
L480449		0.12	<10	<10	45	10	13	0.004
L480450		0.08	<10	<10	56	50	17	0.004
L480451		0.11	<10	<10	55	20	13	0.003
L480452		0.12	<10	<10	41	60	12	0.005
L480453		0.12	<10	<10	54	60	18	0.007
L480454		0.06	<10	<10	60	20	36	0.004
L480455		0.04	<10	<10	58	<10	68	0.209
L480456		0.06	<10	<10	58	50	31	0.006
L480457		0.07	<10	<10	69	30	24	0.006
L480458		0.14	<10	<10	80	30	13	0.004
L480459		0.13	<10	<10	58	50	13	0.006
L480460		0.12	<10	<10	58	30	13	0.005
L480461		0.10	<10	<10	61	160	23	0.006
L480462		0.02	<10	10	52	230	35	0.011
L480463		0.05	<10	<10	42	20	23	0.009
L480464		0.11	<10	<10	66	50	17	0.009
L480465		0.11	<10	<10	44	10	34	0.001
L480466		0.10	<10	<10	45	90	12	0.008
L480467		0.11	<10	<10	39	30	11	0.005
L480468		0.09	<10	10	38	70	9	0.006
L480469		0.11	<10	<10	38	110	10	0.006
L480470		0.11	<10	<10	50	60	14	0.009
L480471		0.11	<10	<10	31	10	9	0.004



ALS Canada Ltd.
 2103 Dollarton Hwy
 North Vancouver BC V7H 0A7
 Téléphone: 604 984 0221 Télécopieur: 604 984 0218
 www.alsglobal.com

À: PAGET MINERALS CORPORATION
 1160 - 1040 W. GEORGIA ST.
 VANCOUVER BC V6E 4H1

Page: 4 - A
 Nombre total de pages: 4 (A - C)
 Finalisée date: 9-AOUT-2011
 Compte: PAGMIN

Projet: Icy Lake

CERTIFICAT D'ANALYSE TR11126835

Description échantillon	Méthode élément unités L.D.	WEI-21	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	
		Poids reçu kg	Ag ppm	Al %	As ppm	B ppm	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	Ga ppm
		0.02	0.2	0.01	2	10	10	0.5	2	0.01	0.5	1	1	1	0.01	10
L480472		4.77	0.4	0.32	3	<10	110	<0.5	21	0.77	<0.5	5	11	438	0.82	<10
L480473		4.51	0.3	0.27	3	<10	190	<0.5	9	0.76	<0.5	4	11	334	0.70	<10
L480474		5.10	0.8	0.30	4	<10	100	<0.5	33	0.85	<0.5	5	17	678	1.02	<10
L480475		0.06	1.7	1.28	14	<10	130	<0.5	2	0.74	0.5	8	32	3450	3.22	<10
L480476		4.44	0.9	0.37	3	<10	80	<0.5	23	1.36	<0.5	8	23	946	1.38	<10
L480477		4.78	0.6	0.51	<2	<10	280	<0.5	10	2.90	<0.5	7	12	692	2.09	<10
L480478		4.50	0.7	0.46	2	<10	240	<0.5	4	1.52	<0.5	6	7	803	1.95	<10
L480479		3.06	0.6	0.48	2	<10	160	<0.5	13	1.90	<0.5	7	5	503	2.58	<10
L480480		4.54	<0.2	0.54	3	<10	480	0.6	15	4.41	<0.5	5	2	332	1.90	<10
L480481		3.40	0.4	0.57	<2	<10	540	0.5	6	3.09	<0.5	7	4	623	2.25	<10
L480482		3.57	0.4	0.50	4	<10	380	0.5	7	3.91	<0.5	7	3	337	2.03	<10
L480483		4.65	0.4	0.49	<2	<10	180	<0.5	2	2.44	<0.5	7	5	681	2.22	<10
L480484		4.78	0.7	0.65	3	<10	410	<0.5	<2	3.14	<0.5	7	4	681	1.99	<10
L480485		0.06	0.3	1.02	3	<10	80	<0.5	<2	0.64	<0.5	7	29	22	1.98	<10
L480486		5.07	0.5	0.67	<2	<10	200	<0.5	2	2.42	<0.5	7	5	433	2.11	<10
L480487		4.84	0.5	0.73	<2	<10	290	<0.5	<2	1.32	<0.5	7	6	329	2.24	<10
L480488		4.54	0.6	0.39	4	<10	270	<0.5	<2	1.09	<0.5	5	7	460	1.61	<10
L480489		4.76	0.9	0.36	3	<10	170	<0.5	3	1.13	<0.5	5	8	672	1.47	<10



ALS Canada Ltd.
 2103 Dollarton Hwy
 North Vancouver BC V7H 0A7
 Téléphone: 604 984 0221 Télécopieur: 604 984 0218
 www.alsglobal.com

À: PAGET MINERALS CORPORATION
 1160 - 1040 W. GEORGIA ST.
 VANCOUVER BC V6E 4H1

Page: 4 - B
 Nombre total de pages: 4 (A - C)
 Finalisée date: 9-AOUT-2011
 Compte: PAGMIN

Projet: Icy Lake

CERTIFICAT D'ANALYSE TR11126835

Description échantillon	Méthode élément unités L.D.	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	
		Hg ppm	K %	La ppm	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	S %	Sb ppm	Sc ppm	Sr ppm	Th ppm
		1	0.01	10	0.01	5	1	0.01	1	10	2	0.01	2	1	1	20
L480472		<1	0.10	10	0.21	73	27	0.09	5	760	7	0.36	<2	1	40	<20
L480473		<1	0.13	10	0.22	78	30	0.08	4	740	8	0.29	<2	1	44	<20
L480474		<1	0.12	10	0.26	79	259	0.08	8	950	7	0.51	<2	1	38	<20
L480475		<1	0.11	<10	0.57	439	299	0.10	29	510	23	0.42	4	5	40	<20
L480476		<1	0.10	10	0.43	133	79	0.08	12	860	4	0.61	<2	3	64	<20
L480477		<1	0.10	20	0.69	370	49	0.06	6	1010	5	0.37	<2	5	468	<20
L480478		<1	0.10	20	0.61	218	35	0.09	2	1210	4	0.50	<2	3	285	<20
L480479		<1	0.10	20	0.57	268	94	0.08	3	1270	7	0.59	<2	4	201	<20
L480480		<1	0.25	20	0.79	501	515	0.05	2	1110	9	0.76	<2	6	1830	<20
L480481		<1	0.18	30	0.59	381	93	0.06	3	1170	3	0.57	<2	6	819	<20
L480482		<1	0.18	20	0.87	460	918	0.06	6	970	14	0.89	<2	5	1410	<20
L480483		<1	0.10	20	0.50	292	123	0.07	3	1150	6	1.00	<2	5	340	<20
L480484		1	0.13	20	0.40	322	156	0.07	3	1080	7	0.96	<2	5	1110	<20
L480485		1	0.06	<10	0.47	304	4	0.05	20	480	2	0.06	<2	4	31	<20
L480486		2	0.09	20	0.49	288	131	0.07	3	1090	4	0.75	<2	4	381	<20
L480487		1	0.13	10	0.80	262	40	0.10	3	1070	8	0.69	<2	3	283	<20
L480488		1	0.09	10	0.42	156	14	0.09	3	1150	5	0.59	<2	2	137	<20
L480489		<1	0.09	10	0.28	136	27	0.08	4	940	5	0.60	<2	2	82	<20



ALS Canada Ltd.
 2103 Dollarton Hwy
 North Vancouver BC V7H 0A7
 Téléphone: 604 984 0221 Télécopieur: 604 984 0218
 www.alsglobal.com

À: PAGET MINERALS CORPORATION
 1160 - 1040 W. GEORGIA ST.
 VANCOUVER BC V6E 4H1

Page: 4 - C
 Nombre total de pages: 4 (A - C)
 Finalisée date: 9-AOUT-2011
 Compte: PAGMIN

Projet: Icy Lake

CERTIFICAT D'ANALYSE TR11126835

Description échantillon	Méthode élément unités L.D.	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	Au-ICP21
		Ti %	Ti ppm	U ppm	V ppm	W ppm	Zn ppm	Au ppm
		0.01	10	10	1	10	2	0.001
L480472		0.11	<10	<10	30	30	10	0.009
L480473		0.12	<10	<10	28	30	9	0.005
L480474		0.12	<10	<10	38	280	10	0.010
L480475		0.12	<10	<10	53	<10	53	1.060
L480476		0.11	<10	<10	52	250	15	0.013
L480477		0.04	<10	<10	60	40	22	0.009
L480478		0.07	<10	<10	56	10	24	0.008
L480479		0.05	<10	<10	64	40	22	0.006
L480480		<0.01	<10	<10	29	<10	17	0.005
L480481		0.01	<10	<10	39	<10	23	0.005
L480482		<0.01	<10	<10	41	<10	21	0.003
L480483		0.03	<10	<10	51	30	22	0.005
L480484		0.02	<10	<10	41	10	20	0.007
L480485		0.11	<10	<10	45	10	34	0.002
L480486		0.03	<10	<10	51	20	19	0.004
L480487		0.08	<10	<10	56	60	20	0.004
L480488		0.10	<10	<10	51	140	11	0.005
L480489		0.09	<10	<10	46	100	11	0.008



ALS Canada Ltd.
2103 Dollarton Hwy
North Vancouver BC V7H 0A7
Téléphone: 604 984 0221 Télécopieur: 604 984 0218
www.alsglobal.com

À: PAGET MINERALS CORPORATION
1160 - 1040 W. GEORGIA ST.
VANCOUVER BC V6E 4H1

Page: 1
Finalisée date: 6-AOUT-2011
Cette copie a fait un rapport sur
9-NOV-2011
Compte: PAGMIN

CERTIFICAT TR11131429

Projet: Icy Lake

Bon de commande #:

Ce rapport s'applique aux 33 échantillons de carotte forage soumis à notre laboratoire de Terrace, BC, Canada le 14-JUIL-2011.

Les résultats sont transmis à:

SONIA JEYACHANDRAN

ROD OGILVIE

DAVID VOLKERT

PRÉPARATION ÉCHANTILLONS

CODE ALS	DESCRIPTION
WEI-21	Poids échantillon reçu
LOG-22	Entrée échantillon - Reçu sans code barre
PUL-QC	Test concassage QC
CRU-31	Granulation - 70 % <2 mm
SPL-21	Échant. fractionné - div. riffles
PUL-31	Pulvérisé à 85 % <75 um
LOG-23	Entrée pulpe - Reçu avec code barre

PROCÉDURES ANALYTIQUES

CODE ALS	DESCRIPTION	INSTRUMENT
Au-ICP21	Au 30 g FA fini ICP-AES	ICP-AES
ME-ICP41	Aqua regia ICP-AES 35 éléments	ICP-AES

À: PAGET MINERALS CORPORATION
ATTN: DAVID VOLKERT
1160 - 1040 W. GEORGIA ST.
VANCOUVER BC V6E 4H1

Ce rapport est final et remplace tout autre rapport préliminaire portant ce numéro de certificat. Les résultats s'appliquent aux échantillons soumis. Toutes les pages de ce rapport ont été vérifiées et approuvées avant publication.

Signature:



Colin Ramshaw, Vancouver Laboratory Manager



ALS Canada Ltd.
2103 Dollarton Hwy
North Vancouver BC V7H 0A7
Téléphone: 604 984 0221 Télécopieur: 604 984 0218
www.alsglobal.com

À: PAGET MINERALS CORPORATION
1160 - 1040 W. GEORGIA ST.
VANCOUVER BC V6E 4H1

Page: 2 - A
Nombre total de pages: 2 (A - C)
Finalisée date: 6-AOUT-2011
Compte: PAGMIN

Projet: Icy Lake

CERTIFICAT D'ANALYSE TR11131429

Description échantillon	Méthode élément unités L.D.	WEI-21	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41
		Poids reçu kg	Ag ppm	Al %	As ppm	B ppm	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	Ga ppm
L480490		4.66	0.4	0.32	3	<10	170	<0.5	4	0.81	<0.5	3	18	440	0.95	<10
L480491		4.94	0.6	0.31	4	<10	190	<0.5	<2	0.91	<0.5	3	8	652	0.95	<10
L480492		4.28	0.5	0.39	4	<10	220	<0.5	<2	0.93	<0.5	4	9	411	1.37	<10
L480493		3.42	0.5	0.59	6	<10	260	<0.5	16	1.36	<0.5	5	6	416	1.93	<10
L480494		4.62	0.7	0.58	4	<10	460	<0.5	4	2.30	<0.5	4	31	630	1.50	<10
L480495		0.05	3.9	1.75	38	<10	120	<0.5	<2	0.98	1.1	18	58	9540	4.41	10
L480496		5.29	0.2	0.49	3	<10	160	<0.5	<2	1.28	<0.5	3	7	165	1.69	<10
L480497		4.98	0.2	0.58	3	<10	330	0.5	<2	3.23	<0.5	4	9	188	1.05	<10
L480498		4.90	0.4	0.39	4	<10	210	<0.5	3	1.15	<0.5	2	3	388	0.82	<10
L480499		4.31	0.2	0.37	3	<10	220	<0.5	<2	1.60	<0.5	3	4	268	0.70	<10
L480500		4.83	0.2	0.28	4	<10	250	<0.5	<2	0.58	<0.5	1	3	183	0.43	<10
L480501		5.19	0.2	0.29	2	<10	260	<0.5	2	0.63	<0.5	1	6	208	0.52	<10
L480502		4.70	<0.2	0.29	2	<10	230	<0.5	<2	0.73	<0.5	2	3	138	0.46	<10
L480503		4.88	0.4	0.32	2	<10	240	<0.5	2	0.73	<0.5	2	4	344	0.48	<10
L480504		5.69	0.6	0.86	6	<10	770	0.5	<2	2.91	<0.5	6	19	625	1.83	<10
L480505		0.05	0.2	1.00	5	<10	80	<0.5	<2	0.60	<0.5	6	30	21	1.90	<10
L480506		4.77	0.6	0.44	4	<10	220	<0.5	4	0.76	<0.5	5	5	507	1.86	<10
L480507		3.50	0.3	0.54	3	<10	300	<0.5	<2	1.12	<0.5	5	5	282	2.23	<10
L480508		4.95	0.4	0.58	19	<10	560	<0.5	3	1.97	<0.5	5	4	367	1.69	<10
L480509		4.74	0.3	0.50	3	<10	340	<0.5	<2	1.31	<0.5	5	5	376	1.70	<10
L480510		4.91	1.0	0.39	4	<10	210	<0.5	<2	0.79	<0.5	5	6	1020	1.45	<10
L480511		4.47	0.6	0.44	2	<10	210	<0.5	5	0.81	<0.5	4	8	522	1.67	<10
L480512		4.50	0.2	0.50	<2	<10	260	<0.5	<2	1.00	<0.5	4	6	277	1.71	<10
L480513		5.12	2.8	0.59	8	<10	260	<0.5	11	1.67	<0.5	5	5	149	2.18	<10
L480514		5.10	0.2	0.46	3	<10	240	<0.5	2	0.90	<0.5	4	11	193	1.63	<10
L480515		0.06	2.1	1.51	28	<10	100	<0.5	4	1.80	0.8	16	62	1900	3.90	<10
L480516		5.10	0.3	0.50	2	<10	330	<0.5	<2	0.99	<0.5	3	6	234	1.74	<10
L480517		4.26	0.3	0.43	3	<10	260	<0.5	2	0.85	<0.5	4	9	88	1.70	<10
L480518		4.82	0.2	0.58	4	<10	300	<0.5	<2	1.34	<0.5	4	7	172	1.79	<10
L480519		4.74	0.3	0.55	<2	<10	350	<0.5	2	1.38	<0.5	5	6	218	1.80	<10
L480520		4.78	0.2	0.46	2	<10	270	<0.5	<2	0.89	<0.5	4	8	225	1.63	<10
L480521		3.89	0.5	0.73	5	<10	240	<0.5	<2	1.72	<0.5	6	7	636	1.88	<10
L480522		3.81	0.8	0.71	4	<10	310	<0.5	11	1.81	<0.5	5	5	367	1.72	<10



ALS Canada Ltd.
 2103 Dollarton Hwy
 North Vancouver BC V7H 0A7
 Téléphone: 604 984 0221 Télécopieur: 604 984 0218
 www.alsglobal.com

À: PAGET MINERALS CORPORATION
 1160 - 1040 W. GEORGIA ST.
 VANCOUVER BC V6E 4H1

Page: 2 - B
 Nombre total de pages: 2 (A - C)
 Finalisée date: 6-AOUT-2011
 Compte: PAGMIN

Projet: Icy Lake

CERTIFICAT D'ANALYSE TR11131429

Description échantillon	Méthode élément unités L.D.	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	
		Hg	K	La	Mg	Mn	Mo	Na	Ni	P	Pb	S	Sb	Sc	Sr	Th
		ppm	%	ppm	%	ppm	ppm	%	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm
		1	0.01	10	0.01	5	1	0.01	1	10	2	0.01	2	1	1	20
L480490		<1	0.15	10	0.21	112	43	0.08	4	750	5	0.33	<2	1	71	<20
L480491		<1	0.11	10	0.19	108	154	0.09	3	840	4	0.39	<2	1	77	<20
L480492		<1	0.11	10	0.29	142	42	0.11	3	960	5	0.42	<2	1	117	<20
L480493		<1	0.09	20	0.57	215	36	0.08	3	990	5	0.47	<2	3	283	<20
L480494		<1	0.12	20	0.62	272	147	0.07	9	1400	5	0.39	<2	3	708	<20
L480495		<1	0.51	10	1.01	517	923	0.11	36	900	41	2.20	8	9	50	<20
L480496		<1	0.10	20	0.48	210	190	0.10	3	960	5	0.34	<2	3	202	<20
L480497		<1	0.15	10	0.42	358	140	0.05	5	840	6	0.15	<2	4	253	<20
L480498		<1	0.11	20	0.23	154	80	0.06	2	860	6	0.19	<2	2	121	<20
L480499		<1	0.13	10	0.33	225	202	0.06	3	880	5	0.16	<2	2	104	<20
L480500		<1	0.17	10	0.15	79	42	0.08	2	910	7	0.10	<2	1	80	<20
L480501		<1	0.15	20	0.16	93	44	0.08	2	950	6	0.16	<2	1	88	<20
L480502		<1	0.13	20	0.17	96	11	0.08	1	1040	7	0.15	<2	1	77	<20
L480503		<1	0.11	20	0.24	93	75	0.08	2	900	5	0.21	<2	1	120	<20
L480504		<1	0.15	20	0.60	339	170	0.06	5	1050	7	0.46	<2	4	621	<20
L480505		<1	0.06	<10	0.45	297	4	0.05	20	490	<2	0.05	<2	4	31	<20
L480506		<1	0.11	10	0.37	144	13	0.09	2	1050	5	0.56	<2	1	202	<20
L480507		<1	0.11	20	0.53	236	80	0.08	3	1120	4	0.33	<2	3	378	<20
L480508		<1	0.17	20	0.35	314	102	0.05	3	790	6	0.49	6	3	456	<20
L480509		<1	0.16	20	0.40	228	23	0.07	3	800	3	0.49	<2	2	264	<20
L480510		<1	0.13	10	0.21	109	120	0.07	2	790	4	0.66	<2	1	83	<20
L480511		<1	0.13	10	0.26	155	99	0.08	2	820	5	0.47	<2	1	84	<20
L480512		<1	0.14	10	0.36	190	45	0.08	2	840	4	0.41	<2	2	176	<20
L480513		<1	0.13	20	0.37	266	23	0.06	2	850	68	0.95	<2	2	249	<20
L480514		<1	0.13	20	0.34	188	7	0.08	2	770	5	0.47	<2	2	149	<20
L480515		<1	0.48	20	0.80	353	159	0.06	16	720	20	1.94	8	6	76	<20
L480516		<1	0.16	20	0.30	253	22	0.08	2	760	5	0.32	<2	2	172	<20
L480517		<1	0.16	20	0.28	227	19	0.08	2	820	15	0.38	<2	1	104	<20
L480518		<1	0.16	20	0.41	283	17	0.07	2	790	4	0.40	<2	3	208	<20
L480519		<1	0.15	20	0.44	313	12	0.07	2	790	4	0.51	<2	3	300	<20
L480520		<1	0.15	10	0.38	216	70	0.08	1	760	5	0.41	<2	2	131	<20
L480521		<1	0.14	20	0.46	259	477	0.06	2	770	9	0.57	<2	3	185	20
L480522		<1	0.14	20	0.52	309	116	0.06	2	740	18	0.39	<2	3	237	<20



ALS Canada Ltd.
 2103 Dollarton Hwy
 North Vancouver BC V7H 0A7
 Téléphone: 604 984 0221 Télécopieur: 604 984 0218
 www.alsglobal.com

À: PAGET MINERALS CORPORATION
 1160 - 1040 W. GEORGIA ST.
 VANCOUVER BC V6E 4H1

Page: 2 - C
 Nombre total de pages: 2 (A - C)
 Finalisée date: 6-AOUT-2011
 Compte: PAGMIN

Projet: Icy Lake

CERTIFICAT D'ANALYSE TR11131429

Description échantillon	Méthode élément unités L.D.	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	Au-ICP21
		Ti %	Ti ppm	U ppm	V ppm	W ppm	Zn ppm	Au ppm
		0.01	10	10	1	10	2	0.001
L480490		0.09	<10	<10	31	60	9	0.005
L480491		0.10	<10	<10	32	40	11	0.007
L480492		0.10	<10	<10	44	30	11	0.003
L480493		0.06	<10	<10	49	10	19	0.005
L480494		0.07	<10	<10	45	20	17	0.005
L480495		0.15	<10	<10	101	20	156	0.458
L480496		0.08	<10	<10	52	10	14	0.002
L480497		0.02	<10	<10	35	20	16	0.002
L480498		0.05	<10	<10	25	10	9	0.007
L480499		0.06	<10	<10	23	40	13	0.004
L480500		0.08	<10	<10	13	10	7	0.003
L480501		0.08	<10	<10	15	10	7	0.003
L480502		0.08	<10	<10	14	10	6	0.002
L480503		0.08	<10	<10	16	20	7	0.004
L480504		0.03	<10	<10	38	10	24	0.006
L480505		0.10	<10	<10	44	10	34	0.001
L480506		0.08	<10	<10	46	10	14	0.004
L480507		0.08	<10	<10	63	130	16	0.003
L480508		0.02	<10	<10	31	<10	20	0.008
L480509		0.06	<10	<10	39	10	14	0.004
L480510		0.08	<10	<10	33	50	17	0.011
L480511		0.09	<10	<10	44	10	14	0.014
L480512		0.09	<10	<10	46	10	12	0.003
L480513		0.05	<10	<10	42	10	14	0.003
L480514		0.08	<10	<10	41	10	11	0.002
L480515		0.04	<10	<10	56	<10	65	0.233
L480516		0.08	<10	<10	44	<10	18	0.002
L480517		0.08	<10	<10	44	10	15	0.001
L480518		0.06	<10	<10	44	10	17	0.003
L480519		0.06	<10	<10	42	<10	17	0.002
L480520		0.08	<10	<10	43	<10	13	0.003
L480521		0.03	<10	<10	43	80	20	0.007
L480522		0.03	<10	<10	41	30	18	0.004



ALS Canada Ltd.
2103 Dollarton Hwy
North Vancouver BC V7H 0A7
Téléphone: 604 984 0221 Télécopieur: 604 984 0218
www.alsglobal.com

À: PAGET MINERALS CORPORATION
1160 - 1040 W. GEORGIA ST.
VANCOUVER BC V6E 4H1

Page: 1
Finalisée date:
25-AOUT-2011
Cette copie a fait un rapport sur
9-NOV-2011
Compte: PAGMIN

CERTIFICAT TR11147259

Projet: Icy Lake

Bon de commande #:

Ce rapport s'applique aux 135 échantillons de carotte forage soumis à notre laboratoire de Terrace, BC, Canada le 28-JUIL-2011.

Les résultats sont transmis à:

SONIA JEYACHANDRAN

ROD OGILVIE

DAVID VOLKERT

PRÉPARATION ÉCHANTILLONS

CODE ALS	DESCRIPTION
WEI-21	Poids échantillon reçu
LOG-22	Entrée échantillon - Reçu sans code barre
CRU-QC	Test concassage QC
PUL-QC	Test concassage QC
CRU-31	Granulation - 70 % <2 mm
SPL-21	Échant. fractionné - div. riffles
PUL-31	Pulvérisé à 85 % <75 um
LOG-23	Entrée pulpe - Reçu avec code barre

PROCÉDURES ANALYTIQUES

CODE ALS	DESCRIPTION	INSTRUMENT
Au-ICP21	Au 30 g FA fini ICP-AES	ICP-AES
ME-ICP41	Aqua regia ICP-AES 35 éléments	ICP-AES

À: PAGET MINERALS CORPORATION
ATTN: DAVID VOLKERT
1160 - 1040 W. GEORGIA ST.
VANCOUVER BC V6E 4H1

Ce rapport est final et remplace tout autre rapport préliminaire portant ce numéro de certificat. Les résultats s'appliquent aux échantillons soumis. Toutes les pages de ce rapport ont été vérifiées et approuvées avant publication.

Signature:



Colin Ramshaw, Vancouver Laboratory Manager



ALS Canada Ltd.

2103 Dollarton Hwy
North Vancouver BC V7H 0A7
Téléphone: 604 984 0221 Télécopieur: 604 984 0218
www.alsglobal.com

À: PAGET MINERALS CORPORATION
1160 - 1040 W. GEORGIA ST.
VANCOUVER BC V6E 4H1

Page: 2 - A
Nombre total de pages: 5 (A - C)

Finalisée date:
25-AOUT-2011
Compte: PAGMIN

Projet: icy Lake

CERTIFICAT D'ANALYSE TR11147259

Description échantillon	Méthode élément unités L.D.	WEI-21	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41
		Poids reçu kg	Ag ppm	Al %	As ppm	B ppm	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	Ga ppm
		0.02	0.2	0.01	2	10	10	0.5	2	0.01	0.5	1	1	1	0.01	10
L480731		9.99	0.6	0.35	6	<10	20	<0.5	<2	1.17	<0.5	6	21	380	1.07	<10
L480732		8.72	2.9	0.56	21	<10	30	<0.5	2	2.85	4.3	11	18	764	1.88	<10
L480733		4.68	1.9	0.47	54	<10	230	<0.5	<2	2.03	1.6	6	12	587	1.47	<10
L480734		4.70	2.6	1.11	75	<10	60	<0.5	<2	4.84	1.6	25	34	1620	3.51	<10
L480735		0.08	1.9	1.49	26	<10	130	<0.5	2	1.78	0.7	16	60	1750	4.04	<10
L480736		4.96	1.6	0.92	31	<10	20	<0.5	<2	2.56	<0.5	14	40	1370	2.59	<10
L480737		4.32	1.6	0.98	37	<10	220	<0.5	<2	3.66	1.0	12	27	832	2.28	<10
L480738		4.83	2.8	1.13	36	<10	100	<0.5	<2	3.51	0.7	11	31	1950	1.85	<10
L480739		4.96	1.0	0.96	21	<10	50	<0.5	<2	2.14	<0.5	13	22	845	3.02	<10
L480740		4.88	0.6	1.65	8	<10	110	<0.5	<2	1.80	<0.5	17	17	536	4.96	10
L480741		4.97	3.5	1.16	77	<10	80	<0.5	<2	2.88	1.0	32	10	2060	4.17	<10
L480742		4.93	0.5	1.25	15	<10	50	<0.5	<2	1.82	<0.5	17	12	513	4.27	10
L480743		5.05	1.0	1.18	15	<10	70	<0.5	<2	2.26	<0.5	17	13	703	3.66	<10
L480744		4.39	0.3	1.70	9	<10	190	<0.5	<2	2.48	<0.5	17	17	218	4.77	10
L480745		0.08	<0.2	1.01	3	<10	70	<0.5	<2	0.64	<0.5	7	28	23	1.98	<10
L480746		5.07	0.6	1.29	21	<10	70	<0.5	<2	3.17	<0.5	18	11	650	4.27	10
L480747		4.97	1.2	1.18	9	<10	80	<0.5	43	2.86	<0.5	14	34	419	2.90	<10
L480748		4.95	2.3	1.31	17	<10	60	<0.5	3	4.72	2.9	13	80	272	3.18	<10
L480749		5.16	0.6	1.29	12	<10	40	<0.5	<2	2.25	<0.5	15	62	394	2.74	<10
L480750		4.89	0.5	0.73	5	<10	50	<0.5	<2	2.31	<0.5	9	28	459	1.83	<10
L480751		5.57	0.6	1.25	6	<10	40	<0.5	5	1.75	<0.5	12	81	390	2.08	<10
L480752		4.39	<0.2	0.77	5	<10	40	<0.5	<2	1.06	<0.5	6	20	139	1.30	<10
L480753		5.69	0.5	0.69	6	<10	40	<0.5	3	1.32	<0.5	6	33	204	1.24	<10
L480754		5.19	0.5	0.67	7	<10	100	<0.5	5	2.49	<0.5	7	27	276	1.33	<10
L480755		0.08	3.6	1.77	32	10	120	<0.5	3	0.98	1.0	18	56	8860	4.54	10
L480756		4.50	0.3	1.54	3	<10	90	<0.5	2	3.72	<0.5	14	122	243	2.51	<10
L480757		5.64	0.2	2.22	4	<10	50	<0.5	<2	2.68	<0.5	15	151	137	2.39	10
L480758		5.69	0.4	1.48	7	<10	40	<0.5	3	1.69	<0.5	14	110	197	2.22	<10
L480759		7.19	0.3	1.25	6	<10	30	<0.5	<2	1.85	<0.5	8	53	187	1.19	<10
L480760		4.12	0.3	0.84	2	<10	30	<0.5	2	1.26	<0.5	4	23	108	0.88	<10
L480761		3.95	0.8	1.45	7	<10	50	<0.5	4	1.71	<0.5	12	109	240	2.21	<10
L480762		5.15	1.3	0.68	6	<10	60	<0.5	17	2.21	<0.5	5	17	154	1.33	<10
L480763		5.71	<0.2	0.84	3	<10	20	<0.5	<2	1.58	<0.5	5	23	39	1.33	<10
L480764		4.98	0.7	0.49	7	<10	30	<0.5	<2	1.01	<0.5	7	20	359	1.27	<10
L480765		0.08	0.2	0.98	2	<10	70	<0.5	<2	0.58	<0.5	6	28	20	1.94	<10
L480766		4.56	1.3	0.72	22	<10	60	<0.5	4	2.62	<0.5	8	47	236	1.51	<10
L480767		5.00	0.8	0.47	6	<10	40	<0.5	2	1.15	<0.5	5	23	299	0.91	<10
L480768		5.25	0.6	0.64	4	<10	40	<0.5	<2	1.01	<0.5	6	28	236	1.05	<10
L480769		4.97	0.6	0.74	7	<10	30	<0.5	3	1.15	<0.5	7	30	250	1.37	<10
L480770		5.19	0.5	1.07	5	<10	30	<0.5	<2	1.76	<0.5	8	74	158	2.01	<10



ALS Canada Ltd.
 2103 Dollarton Hwy
 North Vancouver BC V7H 0A7
 Téléphone: 604 984 0221 Télécopieur: 604 984 0218
 www.alsglobal.com

À: PAGET MINERALS CORPORATION
 1160 - 1040 W. GEORGIA ST.
 VANCOUVER BC V6E 4H1

Page: 2 - B
 Nombre total de pages: 5 (A - C)

Finalisée date:
 25-AOUT-2011
 Compte: PAGMIN

Projet: icy Lake

CERTIFICAT D'ANALYSE TR11147259

Description échantillon	Méthode élément unités L.D.	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	
		Hg ppm	K %	La ppm	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	S %	Sb ppm	Sc ppm	Sr ppm	Th ppm
		1	0.01	10	0.01	5	1	0.01	1	10	2	0.01	2	1	1	20
L480731		<1	0.09	<10	0.47	196	68	0.03	17	670	3	0.35	<2	1	21	<20
L480732		<1	0.12	<10	0.60	485	41	0.03	23	420	362	0.84	10	3	46	<20
L480733		<1	0.10	<10	0.29	480	99	0.01	17	440	70	0.39	49	3	45	<20
L480734		1	0.32	<10	1.30	834	162	0.05	41	600	33	1.03	138	14	89	<20
L480735		<1	0.50	20	0.81	350	152	0.05	17	670	20	1.88	8	6	73	<20
L480736		<1	0.17	<10	1.07	386	84	0.06	43	580	3	0.72	2	7	49	<20
L480737		<1	0.15	<10	0.81	738	243	0.04	39	510	27	0.51	42	7	80	<20
L480738		<1	0.17	<10	0.81	599	77	0.09	27	530	13	0.63	39	6	80	<20
L480739		<1	0.26	<10	0.93	397	363	0.07	38	510	5	0.55	4	8	48	<20
L480740		1	0.70	<10	1.40	457	157	0.12	14	760	2	0.74	<2	12	46	<20
L480741		<1	0.29	<10	0.93	432	187	0.06	19	820	18	1.16	46	13	61	<20
L480742		1	0.35	<10	1.11	392	47	0.09	13	950	3	0.73	2	12	52	<20
L480743		<1	0.36	<10	0.90	378	33	0.09	14	910	3	0.66	<2	12	68	<20
L480744		1	0.54	<10	1.09	503	26	0.06	15	690	<2	0.42	2	16	69	<20
L480745		<1	0.06	<10	0.45	298	6	0.04	20	460	<2	0.05	<2	4	30	<20
L480746		<1	0.26	<10	0.90	486	63	0.06	14	670	5	0.62	3	16	76	<20
L480747		<1	0.24	<10	1.06	339	42	0.10	27	640	15	0.52	<2	8	77	<20
L480748		<1	0.41	<10	1.71	788	162	0.04	34	570	232	0.96	27	10	106	<20
L480749		<1	0.36	<10	1.41	343	89	0.08	26	750	<2	0.44	<2	10	58	<20
L480750		1	0.13	<10	0.84	264	114	0.06	21	740	2	0.45	<2	6	60	<20
L480751		<1	0.28	<10	1.23	261	127	0.13	42	950	7	0.48	<2	5	95	<20
L480752		<1	0.18	<10	0.82	188	55	0.08	14	690	3	0.19	<2	3	72	<20
L480753		<1	0.14	<10	0.85	202	383	0.07	19	690	11	0.27	2	4	60	<20
L480754		<1	0.12	<10	0.64	268	113	0.05	20	650	6	0.35	<2	4	58	<20
L480755		1	0.53	10	1.03	507	919	0.10	34	850	37	2.14	5	9	49	<20
L480756		<1	0.36	<10	1.44	399	169	0.07	52	770	2	0.24	<2	8	97	<20
L480757		<1	0.71	<10	1.78	393	38	0.22	63	970	2	0.20	<2	7	110	<20
L480758		<1	0.49	<10	1.35	325	53	0.15	53	1070	<2	0.30	3	5	57	<20
L480759		1	0.19	<10	0.71	217	17	0.17	31	1030	3	0.16	2	4	90	<20
L480760		<1	0.18	<10	0.56	145	39	0.10	11	540	4	0.05	<2	3	51	<20
L480761		<1	0.39	<10	1.22	303	38	0.16	43	1010	43	0.30	<2	5	63	<20
L480762		<1	0.10	<10	0.64	270	37	0.07	10	450	64	0.28	<2	3	43	<20
L480763		<1	0.13	<10	0.80	231	18	0.09	11	540	4	0.09	<2	4	35	<20
L480764		1	0.12	<10	0.44	153	14	0.08	10	580	26	0.38	<2	2	31	<20
L480765		<1	0.06	<10	0.45	282	3	0.05	19	470	<2	0.04	<2	3	28	<20
L480766		<1	0.14	<10	0.86	400	47	0.09	24	780	131	0.35	3	5	65	<20
L480767		<1	0.14	<10	0.45	136	156	0.07	10	660	26	0.23	<2	2	31	<20
L480768		<1	0.19	<10	0.52	144	112	0.08	13	660	5	0.19	<2	2	34	<20
L480769		<1	0.20	<10	0.68	184	58	0.08	15	740	4	0.29	<2	2	39	<20
L480770		<1	0.23	<10	1.04	295	26	0.10	30	750	5	0.28	<2	4	60	<20



ALS Canada Ltd.
 2103 Dollarton Hwy
 North Vancouver BC V7H 0A7
 Téléphone: 604 984 0221 Télécopieur: 604 984 0218
 www.alsglobal.com

À: PAGET MINERALS CORPORATION
 1160 - 1040 W. GEORGIA ST.
 VANCOUVER BC V6E 4H1

Page: 2 - C
 Nombre total de pages: 5 (A - C)
 Finalisée date:
 25-AOUT-2011
 Compte: PAGMIN

Projet: Icy Lake

CERTIFICAT D'ANALYSE TR11147259

Description échantillon	Méthode élément unités L.D.	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	Au-ICP21
		Ti %	Ti ppm	U ppm	V ppm	W ppm	Zn ppm	Au ppm
		0.01	10	10	1	10	2	0.001
L480731		0.07	<10	<10	30	20	17	0.005
L480732		0.04	<10	<10	37	<10	235	0.013
L480733		0.01	<10	<10	24	<10	116	0.010
L480734		0.07	<10	<10	86	<10	150	0.034
L480735		0.04	<10	<10	55	<10	65	0.224
L480736		0.16	<10	<10	88	<10	43	0.017
L480737		0.06	<10	<10	57	<10	96	0.023
L480738		0.05	<10	<10	60	20	71	0.019
L480739		0.16	<10	<10	112	30	38	0.032
L480740		0.24	<10	<10	200	<10	50	0.011
L480741		0.18	<10	<10	126	<10	89	0.031
L480742		0.27	<10	<10	160	<10	37	0.013
L480743		0.23	<10	<10	131	10	41	0.019
L480744		0.18	<10	<10	161	<10	46	0.004
L480745		0.11	<10	<10	44	10	35	0.001
L480746		0.14	<10	<10	158	<10	43	0.013
L480747		0.19	<10	<10	106	10	28	0.010
L480748		0.12	<10	<10	78	10	229	0.007
L480749		0.28	<10	<10	100	<10	35	0.005
L480750		0.14	<10	<10	73	<10	22	0.005
L480751		0.12	<10	<10	63	<10	26	0.007
L480752		0.14	<10	<10	51	<10	18	0.001
L480753		0.11	<10	<10	50	10	22	0.002
L480754		0.09	<10	<10	50	10	21	0.003
L480755		0.14	<10	<10	99	20	152	0.700
L480756		0.07	<10	<10	75	10	37	0.003
L480757		0.18	<10	<10	85	10	37	0.001
L480758		0.19	<10	<10	70	10	34	0.002
L480759		0.11	<10	<10	46	10	21	0.001
L480760		0.08	<10	<10	43	<10	18	0.001
L480761		0.15	<10	<10	73	10	29	0.003
L480762		0.05	<10	<10	49	<10	21	0.002
L480763		0.08	<10	<10	52	10	20	<0.001
L480764		0.09	<10	<10	37	10	18	0.003
L480765		0.09	<10	<10	42	10	32	0.001
L480766		0.08	<10	<10	49	10	27	0.003
L480767		0.11	<10	<10	34	10	15	0.003
L480768		0.11	<10	<10	37	<10	17	0.002
L480769		0.12	<10	<10	45	30	19	0.003
L480770		0.13	<10	<10	64	10	25	0.002



ALS Canada Ltd.

2103 Dollarton Hwy
 North Vancouver BC V7H 0A7
 Téléphone: 604 984 0221 Télécopieur: 604 984 0218
 www.alsglobal.com

À: PAGET MINERALS CORPORATION
 1160 - 1040 W. GEORGIA ST.
 VANCOUVER BC V6E 4H1

Page: 3 - A
 Nombre total de pages: 5 (A - C)

Finalisée date:
 25-AOUT-2011
 Compte: PAGMIN

Projet: icy Lake

CERTIFICAT D'ANALYSE TR11147259

Description échantillon	Méthode élément unités L.D.	WEI-21	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41
		Poids reçu kg	Ag ppm	Al %	As ppm	B ppm	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	Ga ppm
L480771		5.19	0.4	0.58	6	<10	20	<0.5	<2	0.99	<0.5	7	37	174	1.36	<10
L480772		5.39	0.7	0.53	8	<10	30	<0.5	<2	1.18	<0.5	12	39	408	1.32	<10
L480773		4.83	2.3	0.70	5	<10	40	<0.5	14	1.55	0.5	8	37	479	1.63	<10
L480774		3.56	3.4	0.73	12	<10	30	<0.5	15	1.28	0.6	15	35	1190	1.80	<10
L480775		0.08	1.7	1.20	12	<10	120	<0.5	<2	0.65	<0.5	7	29	3220	3.16	<10
L480776		3.55	0.5	0.65	8	<10	40	<0.5	9	2.02	<0.5	7	28	191	1.59	<10
L480777		5.03	4.3	0.46	53	<10	450	<0.5	6	4.10	9.3	8	20	363	1.81	<10
L480778		5.50	1.1	1.26	9	<10	30	<0.5	13	1.92	<0.5	13	114	342	2.61	10
L480779		5.68	1.0	1.59	12	<10	50	<0.5	5	1.68	<0.5	18	117	467	2.35	<10
L480780		5.52	0.6	0.69	8	<10	30	<0.5	4	1.20	<0.5	9	96	277	1.50	<10
L480781		4.84	2.3	0.64	5	<10	20	<0.5	18	1.91	<0.5	9	52	833	1.38	<10
L480782		5.18	5.0	0.55	3	<10	30	<0.5	22	1.45	<0.5	4	32	510	1.52	<10
L480783		4.67	0.3	0.79	5	<10	30	<0.5	<2	1.59	<0.5	4	31	138	1.21	<10
L480784		6.55	0.3	0.70	7	<10	20	<0.5	4	1.35	<0.5	7	55	168	1.30	<10
L480785		0.08	0.2	1.00	4	<10	70	<0.5	<2	0.60	<0.5	6	29	19	1.96	<10
L480786		4.72	0.2	0.59	5	<10	70	<0.5	2	1.62	<0.5	5	25	126	1.53	<10
L480787		5.06	0.3	0.87	11	<10	30	<0.5	6	1.05	<0.5	6	33	138	1.96	<10
L480788		5.33	0.3	0.68	6	<10	40	<0.5	4	1.56	<0.5	7	41	180	1.80	<10
L480789		5.55	0.7	1.18	6	<10	40	<0.5	2	1.98	1.8	7	59	135	1.63	<10
L480790		3.51	0.5	0.55	3	<10	30	<0.5	2	1.44	<0.5	3	26	164	1.10	<10
L480791		3.02	0.6	0.55	<2	<10	20	<0.5	15	1.52	<0.5	3	17	176	0.97	<10
L480792		5.01	0.3	1.27	7	<10	30	<0.5	4	1.77	<0.5	9	40	166	1.63	<10
L480793		4.78	0.5	1.56	15	<10	50	<0.5	5	1.62	<0.5	13	59	308	2.29	<10
L480794		5.48	<0.2	0.77	7	<10	30	<0.5	<2	1.04	<0.5	5	34	59	1.18	<10
L480795		5.84	7.1	1.80	16	<10	50	<0.5	15	2.39	2.3	15	44	421	3.93	10
L480796		4.10	10.5	1.44	27	<10	150	<0.5	21	6.26	19.0	18	130	551	3.85	<10
L480797		5.28	2.2	1.14	2	<10	40	<0.5	8	3.07	<0.5	10	86	344	2.42	<10
L480798		5.73	0.9	1.57	6	<10	40	<0.5	12	1.79	<0.5	16	48	582	2.79	<10
L480799		5.51	2.4	1.32	6	<10	40	<0.5	25	1.81	0.6	15	19	1545	3.74	<10
L480800		5.43	0.9	1.77	9	<10	60	<0.5	6	2.55	0.5	20	39	857	3.76	10
L480801		5.14	0.5	2.77	13	<10	40	<0.5	3	2.84	<0.5	18	32	320	3.52	10
L480802		6.34	0.9	1.43	23	<10	30	<0.5	<2	2.14	0.5	16	75	562	2.65	<10
L480803		3.17	0.8	1.17	9	<10	30	<0.5	27	1.92	<0.5	11	23	342	2.46	<10
L480804		5.78	0.3	2.22	21	<10	20	<0.5	<2	2.09	<0.5	15	49	227	3.60	10
L480805		0.08	0.2	1.01	2	<10	70	<0.5	2	0.62	<0.5	6	30	19	1.99	<10
L480806		5.05	0.3	1.10	9	<10	30	<0.5	<2	1.53	<0.5	9	29	255	2.53	<10
L480807		5.28	1.6	0.74	20	<10	20	<0.5	8	2.17	<0.5	27	24	1135	3.64	<10
L480808		5.38	0.6	0.75	35	<10	20	<0.5	3	1.61	<0.5	17	58	397	2.04	<10
L480809		5.35	0.5	0.70	10	<10	30	<0.5	2	1.29	<0.5	10	41	239	1.46	<10
L480810		5.02	<0.2	0.74	2	<10	40	<0.5	<2	1.80	<0.5	4	35	41	1.40	<10



ALS Canada Ltd.
 2103 Dollarton Hwy
 North Vancouver BC V7H 0A7
 Téléphone: 604 984 0221 Télécopieur: 604 984 0218
 www.alsglobal.com

À: PAGET MINERALS CORPORATION
 1160 - 1040 W. GEORGIA ST.
 VANCOUVER BC V6E 4H1

Page: 3 - B
 Nombre total de pages: 5 (A - C)

Finalisée date:
 25-AOUT-2011
 Compte: PAGMIN

Projet: icy Lake

CERTIFICAT D'ANALYSE TR11147259

Description échantillon	Méthode élément unités L.D.	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	
		Hg	K	La	Mg	Mn	Mo	Na	Ni	P	Pb	S	Sb	Sc	Sr	Th
		ppm	%	ppm	%	ppm	ppm	%	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm
		1	0.01	10	0.01	5	1	0.01	1	10	2	0.01	2	1	1	20
L480771		<1	0.13	<10	0.53	164	35	0.07	19	640	3	0.30	<2	2	27	<20
L480772		<1	0.16	<10	0.47	149	83	0.07	23	680	2	0.51	<2	2	34	<20
L480773		<1	0.19	<10	0.58	238	82	0.07	15	690	59	0.59	<2	3	49	<20
L480774		<1	0.20	<10	0.70	204	98	0.08	33	790	16	0.85	<2	3	37	<20
L480775		<1	0.10	<10	0.53	402	259	0.08	26	490	19	0.39	3	4	35	<20
L480776		<1	0.12	<10	0.79	276	22	0.06	16	740	9	0.32	<2	5	53	<20
L480777		<1	0.20	<10	0.97	1275	87	0.03	20	580	444	0.67	102	6	187	<20
L480778		1	0.41	<10	1.27	343	21	0.09	35	1090	13	0.45	3	5	53	<20
L480779		1	0.71	<10	1.17	298	23	0.12	56	770	10	0.45	2	4	54	<20
L480780		<1	0.23	<10	0.76	218	41	0.07	48	730	13	0.27	<2	2	26	<20
L480781		<1	0.17	<10	0.64	214	65	0.08	29	880	29	0.40	<2	3	36	<20
L480782		<1	0.15	<10	0.52	194	108	0.06	12	640	189	0.55	<2	3	33	<20
L480783		<1	0.18	<10	0.50	192	128	0.10	12	680	4	0.13	<2	2	46	<20
L480784		<1	0.19	<10	0.72	194	81	0.07	24	780	8	0.17	<2	2	29	<20
L480785		<1	0.06	<10	0.45	284	3	0.06	19	470	<2	0.04	<2	3	29	<20
L480786		<1	0.13	<10	0.49	203	72	0.07	9	620	<2	0.22	<2	2	46	<20
L480787		1	0.19	<10	0.59	190	20	0.10	12	670	<2	0.37	<2	3	44	<20
L480788		1	0.16	<10	0.61	192	93	0.08	18	880	<2	0.31	<2	3	40	<20
L480789		1	0.32	<10	1.04	334	70	0.10	27	790	103	0.18	5	5	51	<20
L480790		<1	0.16	<10	0.48	210	80	0.06	10	630	14	0.18	<2	2	32	<20
L480791		<1	0.15	<10	0.47	164	67	0.07	13	780	15	0.18	<2	2	32	<20
L480792		<1	0.29	<10	0.79	233	49	0.14	45	1020	4	0.18	<2	3	68	<20
L480793		1	0.43	<10	0.99	236	12	0.16	36	990	2	0.30	<2	3	63	<20
L480794		<1	0.20	<10	0.45	149	73	0.10	15	670	<2	0.10	<2	2	36	<20
L480795		1	0.60	<10	1.28	690	75	0.16	22	1120	392	0.53	52	9	75	<20
L480796		<1	0.31	<10	2.15	2550	44	0.05	66	890	1665	1.51	40	12	143	<20
L480797		<1	0.40	<10	1.21	452	33	0.12	33	1520	81	0.52	<2	6	71	<20
L480798		<1	0.45	<10	1.09	309	39	0.17	28	920	5	0.62	<2	5	59	<20
L480799		1	0.43	<10	1.03	373	41	0.14	20	970	8	0.84	<2	7	45	<20
L480800		1	0.81	<10	1.59	517	148	0.10	24	1230	5	0.71	<2	10	46	<20
L480801		<1	0.72	<10	1.37	452	46	0.26	21	1140	3	0.65	2	6	86	<20
L480802		<1	0.38	<10	0.98	307	88	0.11	40	1500	4	0.46	<2	4	51	<20
L480803		<1	0.35	<10	1.40	403	78	0.07	17	1150	10	0.37	<2	4	38	<20
L480804		1	0.33	<10	1.32	482	12	0.13	19	1140	<2	0.28	2	9	75	<20
L480805		<1	0.06	<10	0.46	289	3	0.05	20	470	<2	0.03	<2	3	30	<20
L480806		<1	0.22	<10	0.78	259	34	0.11	14	1120	<2	0.15	<2	6	37	<20
L480807		<1	0.11	<10	0.51	286	81	0.06	31	1270	3	1.17	2	3	37	<20
L480808		<1	0.16	<10	0.57	202	68	0.09	37	1480	5	0.67	<2	3	39	<20
L480809		1	0.21	<10	0.83	241	159	0.07	21	1170	<2	0.24	<2	2	31	<20
L480810		<1	0.24	<10	0.95	358	151	0.07	15	740	13	0.11	<2	3	46	<20



ALS Canada Ltd.
 2103 Dollarton Hwy
 North Vancouver BC V7H 0A7
 Téléphone: 604 984 0221 Télécopieur: 604 984 0218
 www.alsglobal.com

À: PAGET MINERALS CORPORATION
 1160 - 1040 W. GEORGIA ST.
 VANCOUVER BC V6E 4H1

Page: 3 - C
 Nombre total de pages: 5 (A - C)
 Finalisée date:
 25-AOUT-2011
 Compte: PAGMIN

Projet: Icy Lake

CERTIFICAT D'ANALYSE TR11147259

Description échantillon	Méthode élément unités L.D.	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	Au-ICP21
		Ti %	Ti ppm	U ppm	V ppm	W ppm	Zn ppm	Au ppm
		0.01	10	10	1	10	2	0.001
L480771		0.09	<10	<10	38	10	16	0.002
L480772		0.10	<10	<10	38	10	18	0.005
L480773		0.10	<10	<10	53	10	42	0.005
L480774		0.12	<10	<10	53	20	32	0.008
L480775		0.10	<10	<10	49	<10	52	1.075
L480776		0.07	<10	<10	56	20	24	0.003
L480777		<0.01	<10	<10	26	<10	559	0.012
L480778		0.14	<10	<10	83	10	37	0.002
L480779		0.17	<10	<10	80	10	35	0.004
L480780		0.11	<10	<10	40	10	24	0.002
L480781		0.11	<10	<10	45	10	32	0.010
L480782		0.11	<10	<10	46	10	22	0.002
L480783		0.10	<10	<10	43	10	19	0.001
L480784		0.11	<10	<10	45	<10	23	0.001
L480785		0.10	<10	<10	42	10	32	<0.001
L480786		0.10	<10	<10	45	10	17	0.001
L480787		0.12	<10	<10	57	20	18	0.001
L480788		0.11	<10	<10	54	10	17	0.002
L480789		0.13	<10	<10	72	<10	146	0.002
L480790		0.10	<10	<10	39	10	37	0.001
L480791		0.11	<10	<10	37	10	17	0.006
L480792		0.15	<10	<10	48	10	23	0.001
L480793		0.17	<10	<10	61	10	30	0.003
L480794		0.12	<10	<10	46	10	14	<0.001
L480795		0.22	<10	<10	136	50	155	0.011
L480796		0.04	<10	<10	89	130	1220	0.024
L480797		0.16	<10	<10	111	20	43	0.005
L480798		0.20	<10	<10	102	10	34	0.008
L480799		0.25	10	<10	141	20	53	0.014
L480800		0.27	10	<10	138	20	62	0.005
L480801		0.21	<10	<10	119	10	42	0.003
L480802		0.18	<10	<10	103	10	48	0.012
L480803		0.23	<10	<10	105	10	37	0.003
L480804		0.31	<10	<10	143	10	40	0.003
L480805		0.10	<10	<10	44	10	33	<0.001
L480806		0.24	<10	<10	115	10	25	0.006
L480807		0.16	<10	<10	87	10	27	0.015
L480808		0.13	<10	<10	82	10	19	0.005
L480809		0.15	<10	<10	45	<10	18	0.001
L480810		0.14	<10	<10	60	<10	22	<0.001



ALS Canada Ltd.

2103 Dollarton Hwy
 North Vancouver BC V7H 0A7
 Téléphone: 604 984 0221 Télécopieur: 604 984 0218
 www.alsglobal.com

À: PAGET MINERALS CORPORATION
 1160 - 1040 W. GEORGIA ST.
 VANCOUVER BC V6E 4H1

Page: 4 - A
 Nombre total de pages: 5 (A -
 C)

Finalisée date:
 25-AOUT-2011
 Compte: PAGMIN

Projet: Icy Lake

CERTIFICAT D'ANALYSE TR11147259

Description échantillon	Méthode élément unités L.D.	WEI-21 Poids reçu kg	ME-ICP41 Ag ppm	ME-ICP41 Al %	ME-ICP41 As ppm	ME-ICP41 B ppm	ME-ICP41 Ba ppm	ME-ICP41 Be ppm	ME-ICP41 Bi ppm	ME-ICP41 Ca %	ME-ICP41 Cd ppm	ME-ICP41 Co ppm	ME-ICP41 Cr ppm	ME-ICP41 Cu ppm	ME-ICP41 Fe %	ME-ICP41 Ga ppm
		0.02	0.2	0.01	2	10	10	0.5	2	0.01	0.5	1	1	1	0.01	10
L480811		5.63	0.6	1.21	6	<10	30	<0.5	<2	1.82	<0.5	17	27	352	4.78	10
L480812		5.52	0.8	2.10	7	<10	100	<0.5	28	2.89	<0.5	19	41	211	4.83	10
L480813		5.60	0.4	1.15	6	<10	320	<0.5	<2	5.94	<0.5	9	50	114	2.52	<10
L480814		3.22	<0.2	1.39	<2	<10	130	<0.5	<2	4.44	<0.5	9	104	38	2.73	<10
L480815		0.08	1.6	1.25	13	<10	120	<0.5	2	0.68	<0.5	7	30	3230	3.23	<10
L480816		4.36	0.8	1.35	5	<10	80	<0.5	4	2.79	<0.5	21	13	358	5.20	10
L480817		2.73	3.0	1.46	12	<10	150	0.6	13	7.3	9.6	10	8	190	3.76	<10
L480818		5.01	0.2	2.14	5	<10	30	0.5	<2	5.88	<0.5	11	48	226	3.41	<10
L480819		4.42	2.4	2.90	6	<10	50	<0.5	3	4.61	6.4	18	34	736	4.43	10
L480820		5.53	3.0	2.36	36	<10	190	0.7	4	9.6	12.9	16	21	198	5.22	<10
L480821		5.35	1.1	1.51	9	<10	20	<0.5	5	4.77	<0.5	13	38	799	5.68	10
L480822		5.75	0.5	1.69	6	<10	30	<0.5	3	2.35	<0.5	12	36	132	3.44	10
L480823		5.36	0.3	0.81	4	<10	30	<0.5	4	1.75	<0.5	7	5	206	2.17	<10
L480824		4.07	0.5	1.00	8	<10	20	<0.5	4	1.99	<0.5	8	7	232	2.45	<10
L480825		0.08	0.2	1.04	5	<10	70	<0.5	<2	0.63	<0.5	6	30	20	1.99	<10
L480826		4.60	0.4	0.83	3	<10	30	<0.5	2	1.72	<0.5	5	23	239	1.70	<10
L480827		1.58	0.5	0.35	4	<10	40	<0.5	6	1.68	<0.5	1	5	39	0.45	<10
L480828		5.43	2.4	2.04	5	<10	70	<0.5	46	1.99	<0.5	9	110	217	2.56	10
L480829		3.15	<0.2	1.31	8	<10	50	<0.5	8	1.43	<0.5	10	107	182	2.57	<10
L480830		2.02	0.2	0.34	<2	<10	40	<0.5	<2	1.33	<0.5	2	13	49	0.53	<10
L480831		3.71	0.2	1.68	7	<10	60	<0.5	2	1.56	<0.5	8	23	161	2.69	10
L480832		3.40	0.3	1.26	3	<10	50	<0.5	<2	1.65	<0.5	11	28	249	2.63	<10
L480833		3.53	0.2	0.71	<2	<10	120	<0.5	2	1.96	<0.5	6	4	300	1.37	<10
L480834		3.80	0.3	0.60	<2	<10	80	<0.5	<2	2.03	<0.5	4	4	195	1.10	<10
L480835		0.08	1.8	1.42	25	<10	120	<0.5	<2	1.74	0.9	16	60	1725	3.88	<10
L480836		5.19	0.3	1.31	<2	<10	70	<0.5	<2	2.69	<0.5	11	72	330	2.57	<10
L480837		4.91	<0.2	1.00	<2	<10	70	<0.5	<2	2.18	<0.5	5	35	110	1.32	<10
L480838		5.32	<0.2	1.63	<2	<10	140	<0.5	<2	2.26	<0.5	8	43	260	2.39	<10
L480839		5.36	<0.2	1.48	<2	<10	80	<0.5	3	5.21	<0.5	9	55	74	2.38	<10
L480840		5.29	0.2	1.34	<2	<10	90	<0.5	2	4.56	<0.5	11	84	361	2.78	<10
L480841		6.55	<0.2	2.01	<2	<10	180	<0.5	<2	2.04	<0.5	12	146	178	2.43	10
L480842		1.62	0.3	0.36	2	<10	50	<0.5	<2	0.91	<0.5	4	5	306	0.60	<10
L480843		5.80	0.3	1.05	3	<10	50	<0.5	2	1.27	<0.5	8	33	319	2.48	<10
L480844		4.07	0.3	0.91	9	<10	30	<0.5	3	1.43	<0.5	10	46	705	2.77	<10
L480845		0.08	0.4	0.99	<2	<10	70	<0.5	2	0.61	<0.5	8	30	22	1.92	<10
L480846		4.88	0.3	0.31	<2	<10	190	<0.5	5	0.95	<0.5	3	4	155	0.41	<10
L480847		5.55	0.7	0.95	8	<10	40	<0.5	11	1.77	<0.5	10	31	681	2.66	<10
L480848		1.20	<0.2	0.39	<2	<10	90	<0.5	3	1.97	<0.5	3	6	180	0.73	<10
L480849		4.47	0.2	1.34	<2	<10	110	<0.5	96	1.00	<0.5	9	37	287	2.62	<10
L480850		4.25	0.2	0.91	<2	<10	110	<0.5	5	1.00	<0.5	8	23	209	2.47	<10



ALS Canada Ltd.
 2103 Dollarton Hwy
 North Vancouver BC V7H 0A7
 Téléphone: 604 984 0221 Télécopieur: 604 984 0218
 www.alsglobal.com

À: PAGET MINERALS CORPORATION
 1160 - 1040 W. GEORGIA ST.
 VANCOUVER BC V6E 4H1

Page: 4 - B
 Nombre total de pages: 5 (A - C)
 Finalisée date:
 25-AOUT-2011
 Compte: PAGMIN

Projet: Icy Lake

CERTIFICAT D'ANALYSE TR11147259

Description échantillon	Méthode élément unités L.D.	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	
		Hg	K	La	Mg	Mn	Mo	Na	Ni	P	Pb	S	Sb	Sc	Sr	Th
		ppm	%	ppm	%	ppm	ppm	%	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm
L480811	<1	0.30	<10	1.16	464	47	0.11	12	780	<2	0.75	3	8	39	<20	
L480812	<1	0.61	<10	1.87	867	34	0.14	20	900	19	0.84	<2	14	91	<20	
L480813	<1	0.27	<10	1.88	669	164	0.04	32	770	28	0.20	9	10	194	<20	
L480814	1	0.45	10	1.82	592	162	0.07	39	880	3	0.05	<2	12	109	<20	
L480815	<1	0.10	<10	0.55	414	287	0.09	28	500	18	0.40	3	4	37	<20	
L480816	1	0.32	<10	1.27	732	33	0.09	9	1170	<2	0.93	<2	16	56	<20	
L480817	1	0.25	<10	1.96	1165	223	0.03	16	680	201	0.94	17	10	152	<20	
L480818	<1	0.41	<10	1.53	729	373	0.13	38	1150	<2	0.30	4	14	127	<20	
L480819	1	0.81	<10	1.78	935	17	0.26	19	950	317	0.52	2	17	114	<20	
L480820	<1	0.45	<10	2.26	1695	7	0.07	21	860	383	0.55	51	16	193	<20	
L480821	<1	0.31	<10	1.20	901	92	0.10	23	930	6	0.58	<2	8	54	<20	
L480822	<1	0.31	<10	1.16	467	46	0.17	19	1540	12	0.22	<2	10	60	<20	
L480823	<1	0.17	10	0.65	257	80	0.12	6	1720	3	0.29	<2	5	39	<20	
L480824	<1	0.19	<10	0.95	291	93	0.09	9	1640	3	0.35	<2	6	31	<20	
L480825	<1	0.06	<10	0.46	290	3	0.06	20	480	<2	0.03	<2	4	30	<20	
L480826	<1	0.17	<10	0.60	198	148	0.09	11	1490	2	0.34	<2	5	31	<20	
L480827	<1	0.14	10	0.20	110	68	0.06	3	870	37	0.09	<2	1	29	<20	
L480828	1	0.55	<10	1.32	277	14	0.15	33	780	187	0.54	<2	6	75	<20	
L480829	<1	0.50	<10	1.31	286	31	0.11	36	1100	<2	0.35	<2	5	35	<20	
L480830	<1	0.15	10	0.28	123	29	0.06	4	940	7	0.06	<2	1	28	<20	
L480831	<1	0.56	<10	1.41	331	35	0.14	15	1450	2	0.26	<2	7	57	<20	
L480832	1	0.46	<10	1.41	355	88	0.10	18	890	3	0.37	<2	7	41	<20	
L480833	<1	0.11	20	0.75	278	159	0.05	6	840	6	0.33	<2	5	80	<20	
L480834	<1	0.12	20	0.64	276	18	0.05	5	830	5	0.23	<2	4	59	<20	
L480835	<1	0.46	20	0.80	343	148	0.04	15	660	19	1.78	7	6	71	<20	
L480836	<1	0.60	<10	1.45	378	38	0.07	38	1040	6	0.28	<2	8	61	<20	
L480837	<1	0.18	10	1.12	286	26	0.11	15	1170	3	0.09	<2	5	71	<20	
L480838	<1	0.28	10	1.95	352	24	0.13	19	1550	5	0.10	<2	10	96	<20	
L480839	1	0.32	<10	1.69	567	10	0.07	27	1150	3	0.10	<2	14	110	<20	
L480840	1	0.41	<10	1.39	511	48	0.06	30	1470	5	0.23	<2	11	97	<20	
L480841	1	0.82	<10	1.58	338	19	0.18	57	1240	2	0.19	<2	6	76	<20	
L480842	<1	0.13	10	0.21	91	81	0.06	4	890	9	0.25	<2	1	38	<20	
L480843	<1	0.44	10	0.88	224	35	0.09	15	1490	3	0.21	<2	5	35	<20	
L480844	<1	0.15	10	0.66	202	36	0.08	22	1600	3	0.22	<2	4	31	<20	
L480845	<1	0.06	<10	0.46	296	4	0.03	20	470	2	0.04	<2	3	30	<20	
L480846	<1	0.17	10	0.16	87	14	0.05	3	1000	11	0.20	<2	1	69	<20	
L480847	1	0.30	10	0.81	242	28	0.08	16	1110	3	0.35	<2	6	49	<20	
L480848	<1	0.14	10	0.36	181	17	0.04	4	900	6	0.10	<2	3	47	<20	
L480849	<1	0.72	10	1.12	264	29	0.13	18	930	7	0.29	<2	7	46	<20	
L480850	<1	0.43	10	0.80	238	19	0.11	11	1020	3	0.17	<2	5	35	<20	



ALS Canada Ltd.
 2103 Dollarton Hwy
 North Vancouver BC V7H 0A7
 Téléphone: 604 984 0221 Télécopieur: 604 984 0218
 www.alsglobal.com

À: PAGET MINERALS CORPORATION
 1160 - 1040 W. GEORGIA ST.
 VANCOUVER BC V6E 4H1

Page: 4 - C
 Nombre total de pages: 5 (A - C)

Finalisée date:
 25-AOUT-2011
 Compte: PAGMIN

Projet: Icy Lake

CERTIFICAT D'ANALYSE TR11147259

Description échantillon	Méthode élément unités L.D.	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	Au-ICP21
		Ti %	Ti ppm	U ppm	V ppm	W ppm	Zn ppm	Au ppm
		0.01	10	10	1	10	2	0.001
L480811		0.24	<10	<10	165	10	36	0.003
L480812		0.24	<10	<10	188	10	70	0.002
L480813		0.02	<10	<10	77	<10	59	0.001
L480814		0.10	<10	<10	98	<10	38	<0.001
L480815		0.11	<10	<10	50	<10	53	0.917
L480816		0.13	<10	<10	164	<10	53	0.003
L480817		<0.01	<10	<10	56	<10	661	0.009
L480818		0.07	<10	<10	109	<10	45	0.003
L480819		0.20	<10	<10	159	<10	458	0.002
L480820		0.02	<10	<10	104	<10	759	0.014
L480821		0.19	<10	<10	122	10	49	0.011
L480822		0.23	<10	<10	113	20	33	0.001
L480823		0.28	<10	<10	81	20	18	0.004
L480824		0.27	<10	<10	92	10	24	0.002
L480825		0.11	<10	<10	44	10	33	<0.001
L480826		0.26	<10	<10	82	10	17	0.003
L480827		0.10	<10	<10	22	10	11	<0.001
L480828		0.25	<10	<10	119	<10	51	0.001
L480829		0.25	10	<10	105	10	29	0.004
L480830		0.10	<10	<10	22	<10	10	<0.001
L480831		0.24	<10	<10	120	10	31	0.003
L480832		0.22	<10	<10	121	<10	31	0.003
L480833		0.05	<10	<10	54	<10	20	0.007
L480834		0.05	<10	<10	48	<10	17	0.003
L480835		0.04	<10	<10	54	<10	62	0.248
L480836		0.20	<10	<10	114	<10	36	0.010
L480837		0.17	<10	<10	73	10	19	0.003
L480838		0.23	<10	<10	119	<10	32	0.009
L480839		0.14	<10	<10	112	<10	35	0.002
L480840		0.10	<10	<10	118	<10	39	0.010
L480841		0.25	<10	<10	119	<10	34	0.004
L480842		0.08	<10	<10	19	<10	12	0.009
L480843		0.26	<10	<10	120	<10	28	0.010
L480844		0.23	<10	<10	120	<10	29	0.032
L480845		0.10	<10	<10	44	10	33	<0.001
L480846		0.09	<10	<10	15	<10	10	0.006
L480847		0.20	<10	<10	118	10	41	0.012
L480848		0.08	<10	<10	40	<10	12	0.001
L480849		0.26	<10	<10	125	<10	37	0.004
L480850		0.25	<10	<10	133	<10	27	0.006



ALS Canada Ltd.
 2103 Dollarton Hwy
 North Vancouver BC V7H 0A7
 Téléphone: 604 984 0221 Télécopieur: 604 984 0218
 www.alsglobal.com

À: PAGET MINERALS CORPORATION
 1160 - 1040 W. GEORGIA ST.
 VANCOUVER BC V6E 4H1

Page: 5 - A
 Nombre total de pages: 5 (A - C)

Finalisée date:
 25-AOUT-2011
 Compte: PAGMIN

Projet: Icy Lake

CERTIFICAT D'ANALYSE TR11147259

Description échantillon	Méthode élément unités L.D.	WEI-21	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41
		Poids reçu kg	Ag ppm	Al %	As ppm	B ppm	Ba ppm	Be ppm	Bi ppm	Ca %	Cd ppm	Co ppm	Cr ppm	Cu ppm	Fe %	Ga ppm
		0.02	0.2	0.01	2	10	10	0.5	2	0.01	0.5	1	1	1	0.01	10
L480851		3.99	0.2	0.72	<2	<10	100	<0.5	4	1.01	<0.5	5	24	171	1.30	<10
L480852		3.47	0.9	1.06	10	<10	20	<0.5	5	1.82	<0.5	5	7	215	1.88	<10
L480853		3.60	0.3	0.85	4	<10	30	<0.5	2	1.70	<0.5	5	25	131	2.28	<10
L480854		3.21	0.7	0.51	2	<10	120	<0.5	7	1.76	<0.5	4	16	206	0.97	<10
L480855		0.07	1.5	1.25	15	<10	120	<0.5	<2	0.70	0.5	8	31	3330	3.16	<10
L480856		3.35	0.4	0.54	3	<10	210	<0.5	3	2.08	<0.5	3	7	138	0.75	<10
L480857		4.88	<0.2	1.40	2	<10	120	<0.5	2	0.79	<0.5	10	162	188	2.18	<10
L480858		5.02	0.4	0.90	<2	<10	60	<0.5	4	1.20	<0.5	7	18	158	1.68	<10
L480859		4.79	<0.2	1.18	2	<10	60	<0.5	2	1.63	<0.5	12	2	121	3.12	<10
L480860		5.51	3.4	0.86	13	<10	150	<0.5	13	3.79	0.5	6	10	151	1.66	<10
L480861		4.91	3.4	0.93	6	<10	50	<0.5	3	2.61	0.7	15	16	3670	3.69	<10
L480862		5.59	0.9	1.41	2	<10	30	<0.5	<2	1.57	<0.5	10	44	2160	2.04	<10
L480863		5.80	0.6	1.97	4	<10	90	<0.5	2	1.70	<0.5	11	60	1375	2.64	10
L480864		6.35	0.4	1.42	<2	<10	100	<0.5	<2	1.12	<0.5	9	29	809	1.89	10
L480865		0.08	0.2	1.00	<2	<10	70	<0.5	<2	0.62	<0.5	7	29	24	1.92	<10



ALS Canada Ltd.
 2103 Dollarton Hwy
 North Vancouver BC V7H 0A7
 Téléphone: 604 984 0221 Télécopieur: 604 984 0218
 www.alsglobal.com

À: PAGET MINERALS CORPORATION
 1160 - 1040 W. GEORGIA ST.
 VANCOUVER BC V6E 4H1

Page: 5 - B
 Nombre total de pages: 5 (A - C)

Finalisée date:
 25-AOUT-2011
 Compte: PAGMIN

Projet: Icy Lake

CERTIFICAT D'ANALYSE TR11147259

Description échantillon	Méthode élément unités L.D.	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	
		Hg ppm	K %	La ppm	Mg %	Mn ppm	Mo ppm	Na %	Ni ppm	P ppm	Pb ppm	S %	Sb ppm	Sc ppm	Sr ppm	Th ppm
		1	0.01	10	0.01	5	1	0.01	1	10	2	0.01	2	1	1	20
L480851		<1	0.41	10	0.60	175	15	0.07	9	970	6	0.18	<2	3	42	<20
L480852		<1	0.11	<10	0.31	138	13	0.11	7	1200	83	0.27	<2	2	69	<20
L480853		<1	0.26	10	0.66	214	10	0.09	12	1200	29	0.29	<2	3	50	<20
L480854		<1	0.15	10	0.54	230	12	0.05	7	960	20	0.23	<2	3	58	<20
L480855		<1	0.10	<10	0.55	424	296	0.07	29	500	20	0.41	2	4	38	<20
L480856		<1	0.17	10	0.46	234	9	0.03	5	890	12	0.14	2	3	89	<20
L480857		<1	0.91	<10	1.50	249	13	0.08	37	700	2	0.10	3	6	34	<20
L480858		<1	0.51	10	0.90	213	18	0.07	10	1050	7	0.25	<2	4	35	<20
L480859		<1	0.66	10	1.37	327	15	0.08	11	1630	6	0.25	<2	9	37	<20
L480860		<1	0.34	10	1.32	1150	60	0.04	12	1010	112	0.54	25	8	132	<20
L480861		1	0.35	<10	0.96	417	350	0.06	20	1020	19	0.92	<2	9	55	<20
L480862		<1	0.24	10	0.69	156	252	0.13	26	980	2	0.39	2	4	55	<20
L480863		<1	0.82	<10	1.59	266	70	0.11	28	810	<2	0.30	<2	7	43	<20
L480864		<1	0.68	<10	1.14	184	32	0.08	20	870	3	0.21	<2	5	36	<20
L480865		<1	0.06	<10	0.46	296	4	0.04	20	460	2	0.04	<2	3	30	<20



ALS Canada Ltd.
 2103 Dollarton Hwy
 North Vancouver BC V7H 0A7
 Téléphone: 604 984 0221 Télécopieur: 604 984 0218
 www.alsglobal.com

À: PAGET MINERALS CORPORATION
 1160 - 1040 W. GEORGIA ST.
 VANCOUVER BC V6E 4H1

Page: 5 - C
 Nombre total de pages: 5 (A - C)

Finalisée date:
 25-AOUT-2011
 Compte: PAGMIN

Projet: Icy Lake

CERTIFICAT D'ANALYSE TR11147259

Description échantillon	Méthode élément unités L.D.	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	ME-ICP41	Au-ICP21
		Ti %	Ti ppm	U ppm	V ppm	W ppm	Zn ppm	Au ppm
		0.01	10	10	1	10	2	0.001
L480851		0.16	<10	<10	58	<10	18	0.003
L480852		0.16	<10	<10	76	10	14	0.005
L480853		0.17	<10	<10	94	10	21	0.004
L480854		0.12	<10	<10	52	<10	16	0.005
L480855		0.11	<10	<10	51	<10	56	0.996
L480856		0.05	<10	<10	34	<10	17	0.003
L480857		0.23	<10	<10	101	<10	32	0.005
L480858		0.23	<10	<10	94	10	26	0.001
L480859		0.35	<10	<10	203	<10	42	0.002
L480860		0.12	<10	<10	68	30	41	0.049
L480861		0.21	<10	<10	148	<10	80	0.158
L480862		0.25	<10	<10	116	<10	43	0.139
L480863		0.27	<10	<10	141	<10	55	0.072
L480864		0.23	<10	<10	102	<10	40	0.045
L480865		0.10	<10	<10	43	10	32	<0.001